

Cite this: *J. Mater. Chem. C*, 2022,
10, 16321

Triplet transfer from PbS quantum dots to tetracene ligands: is faster always better?†

Victor Gray,^{ib}*^{ab} William Drake,^a Jesse R. Allardice,^a Zhilong Zhang,^{ib}^a
James Xiao,^a Daniel G. Congrave,^c Jeroen Royakkers,^{ib}^c Weixuan Zeng,^{ib}^c
Simon Dowland,^d Neil C. Greenham,^{ib}^a Hugo Bronstein,^{ib}^c John E. Anthony^{ib}^e
and Akshay Rao*^a

Quantum dot-organic semiconductor hybrid materials are gaining increasing attention as spin mixers for applications ranging from solar harvesting to spin memories. Triplet energy transfer between the inorganic quantum dot (QD) and organic semiconductor is a key step to understand in order to develop these applications. Here we report on the triplet energy transfer from PbS QDs to four energetically and structurally similar tetracene ligands. Even with similar ligands we find that the triplet energy transfer dynamics can vary significantly. For TIPS-tetracene derivatives with carboxylic acid, acetic acid and methanethiol anchoring groups on the short pro-cata side we find that triplet transfer occurs through a stepwise process, mediated *via* a surface state, whereas for monosubstituted TIPS-tetracene derivative 5-(4-benzoic acid)-12-triisopropylsilylethynyl tetracene (BAT) triplet transfer occurs directly, albeit slower, *via* a Dexter exchange mechanism. Even though triplet transfer is slower with BAT the overall yield is greater, as determined from upconverted emission using rubrene emitters. This work highlights that the surface-mediated transfer mechanism is plagued with parasitic loss pathways and that materials with direct Dexter-like triplet transfer are preferred for high-efficiency applications.

Received 17th August 2022,
Accepted 28th September 2022

DOI: 10.1039/d2tc03470k

rsc.li/materials-c

Introduction

Organic-inorganic semiconductor nanocomposites often benefit from combining specific properties from each material type, resulting in materials with properties spanning a wider range of uses. For example, one class of organic-inorganic semiconductor nanocomposites exploit the different spin properties of organic and inorganic semiconductors. By combining a material with ill-defined spin states and a small exchange splitting (typically inorganic nanomaterials) with a material with well-defined spin states and a much larger exchange splitting (typically organic semiconductors), materials that are suitable for spin conversion and spin-mixing can be obtained. Recently these spin-mixing materials have gained increasing

attention for applications such as solar energy harvesting, triplet sensitization, photon management and spin memories.¹⁻⁷

Different types of inorganic nanomaterials, such as perovskite nanocrystals and films,⁸⁻¹⁵ chalcogenide QDs and platelets,^{1,16-25} as well as CuInS₂²⁶ QDs have all been combined with organic semiconductors to achieve either singlet-to-triplet and triplet-to-singlet spin conversion. Due to the small exchange splitting in inorganic nanomaterials spin-mixing occurs in the inorganic part, with the organic semiconductor functioning as a triplet acceptor or donor depending on the direction of exciton transfer. Hence, a key part of the overall spin-mixing process is the transfer of a triplet exciton from (to) an inorganic nanomaterial to (from) the organic semiconductor. A schematic illustration of triplet exciton transfer from a photoexcited PbS QD to an organic ligand is shown in Fig. 1a.

Interestingly, the mechanism for triplet exciton transfer in these nanocomposites varies between structures, leading to some confusion. Recently, multiple studies have tried to address these issues by shedding light on what governs these different mechanisms of triplet exciton transfer. Currently, three different mechanisms are identified for triplet exciton transfer across organic-inorganic interfaces; The first is a direct Dexter type exchange mechanism where the whole exciton (electron and hole) transfers simultaneously across the organic-inorganic interface.^{14,20} The second is a stepwise

^a Cavendish Laboratory, University of Cambridge, J. J. Thomson Avenue, Cambridge, CB3 0HE, UK. E-mail: victor.gray@kemi.uu.se, ar525@cam.ac.uk

^b Department of Chemistry - Ångström Laboratory, Uppsala University, Box 523, 751 20, Uppsala, Sweden

^c Department of Chemistry, University of Cambridge, Lensfield Road, Cambridge, CB2 1EW, UK

^d Cambridge Photon Technology, J. J. Thomson Avenue, Cambridge, CB3 0HE, UK

^e University of Kentucky Center for Applied Energy Research, 2582 Research Park Dr, Lexington Kentucky, 40511, USA

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2tc03470k>



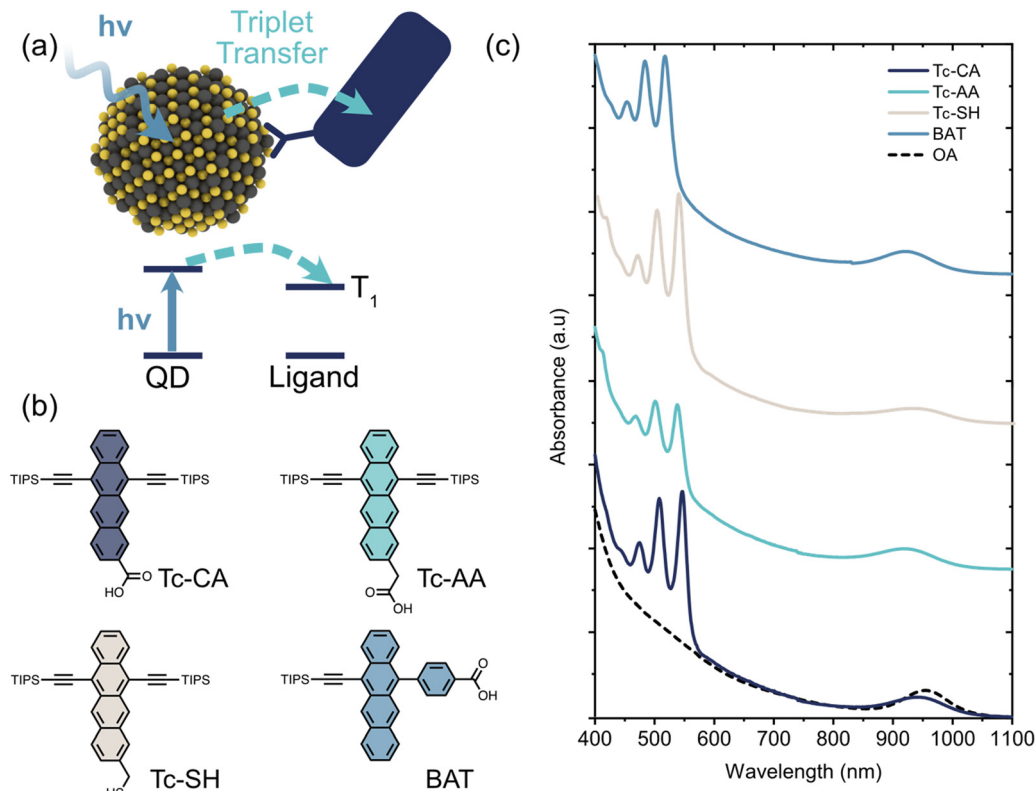


Fig. 1 (a) Schematic illustration of the triplet sensitization process studied herein. A quantum dot (QD) absorbs a photon whereupon the exciton is transferred to an energetically available triplet state on a surface-anchored organic ligand. (b) Molecular structures of the four tetracene based ligands used as triplet acceptors. (c) Absorption spectra of the PbS/ligand QDs used in this study, compared to the as synthesized oleic acid (OA)-capped PbS QDs.

charge-transfer-mediated mechanism that can occur if the band alignment is suitable.^{14,15} Here the hole (or electron) is first transferred across the interface, followed by the electron (hole) at a later time, completing the transfer. The third mechanism is also stepwise, however, in this case the intermediate state is found to be a surface trap state on the inorganic QD, localizing the hole to the surface before transfer to the organic semiconductor is completed.^{27,28}

Usually, the studies detailing the different mechanisms cover one or two specific material combinations and comparison between studies is difficult as they often deal with structurally and energetically different materials. Hence, it can be difficult to draw general conclusions regarding what governs the mechanism. Therefore, we choose to study four structurally similar tetracene ligands attached to a high-energy PbS QD to better understand the differences in triplet transfer mechanisms from QD to ligand and how it relates to ligand structure. We chose to study ligands with different binding motifs (carboxylic acid and thiol), different spacers (no spacer, CH₂ and phenyl) as well as different attachment points to the ligand core. We previously showed that SH anchors improve the thermal stability of the QD-ligand complex without affecting the triplet transfer efficiency of ligand to QD triplet transfer.²⁹ Rigid spacers on the other hand have been shown to decrease the triplet transfer efficiency.^{30–32} Here we observe a stepwise

surface-trap-mediated triplet transfer mechanism in three of the QD/ligand systems and a direct, albeit slower, transfer in the fourth QD/ligand system. Interestingly, the slower direct mechanism results in a higher triplet transfer efficiency as manifested in a significantly higher triplet-sensitized upconversion (UC) emission from rubrene. Based on our observations we conclude that the surface-state-mediated transfer also leads to significant losses and should be avoided in high efficiency devices.

Results and discussion

PbS quantum dots with an exciton absorption peak at 954 nm (1.3 eV) were synthesized as described previously (see ESI† for details). As triplet acceptor ligands we choose to investigate three 6,11-bis-triisopropylsilylethynyl tetracene (TIPS-Tc) derivatives and one monosubstituted 5-(4-benzoic acid)-12-triisopropylsilylethynyl tetracene (BAT) derivative, Fig. 1. The three TIPS-Tc derivatives have different anchoring groups; carboxylic acid (Tc-CA), acetic acid (Tc-AA) and thiol (Tc-SH), however all three derivatives attach to the QD from the tetracene short (*pro-cata*) side. The fourth derivative, 4-(12-((triisopropylsilyl)ethynyl)tetracen-5-yl)benzoic acid (BAT), on the other hand, has the benzoic acid anchoring group attached to



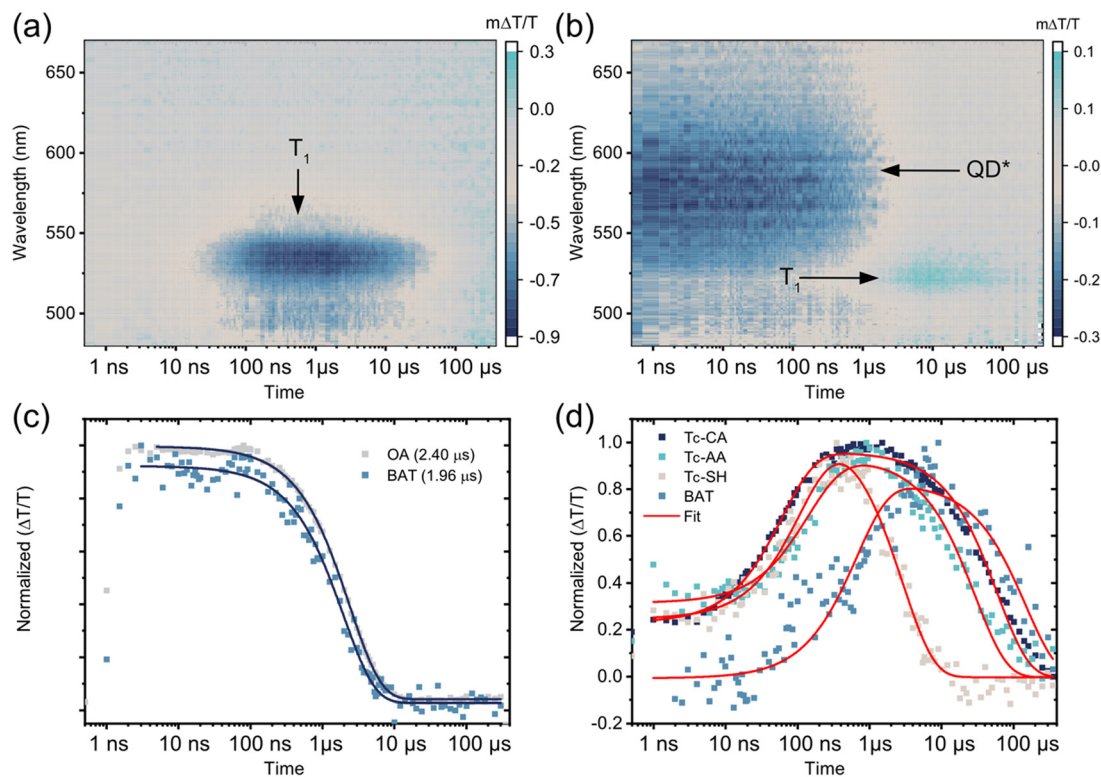


Fig. 2 (a) ns-resolved transient absorption (TA) 2D map of PbS/Tc-CA showing no QD features but a delayed formation of Tc-CA triplet photoinduced absorption (PIA) at 525–550 nm. (b) ns-resolved TA 2D map of PbS/BAT with QD PIA features at 525–625 nm decaying and a correlated formation of BAT ground state bleach (GSB) at 525 nm. (c) Comparison of the normalized transient absorption signal of PbS/OA at the GSB (950 nm) with the GSB signal of PbS/BAT showing a 20% quenching of the QD lifetime. (d) Comparison of the ligand triplet formation dynamics. For Tc-CA, Tc-AA and Tc-SH the dynamics is monitored directly at 525–535 nm. For BAT the dynamics at 520–530 nm is corrected by removing contribution of the QD PIA decay. Fits are a rise term consisting of a sum of exponential decays assuming a Poisson distribution of bound ligands and a monoexponential decay component. All samples were excited at 700 nm with 400 nJ per pulse.

What governs the balance between the different mechanisms is still an area of debate and ongoing research. However, the most recent observations point at two different stepwise mechanisms and one direct Dexter-like mechanism. Depending on the binding geometry of the ligand and the extent of quantum confinement of the QD, the direct Dexter-like mechanism has been shown to be mediated by different coupling mechanisms:³⁷ For highly quantum confined QDs and *peri*-substituted acene ligands Dexter transfer is mediated by through space coupling whereas *pro-cata* substituted acenes are better suited for less quantum confined QDs where transfer is mediated by a through bond coupling.³⁷ The direct mechanism has further been suggested to possibly be mediated by a virtual charge-transfer state.¹⁴ On the other hand, for the two stepwise mechanisms the difference is that they invoke two different intermediate states. The first mechanism, referred to as the charge-transfer-mediated triplet transfer, has been shown to occur when the ligand and QD band alignment favours hole or electron transfer.^{14,15,33} In this case, the hole (electron) is transferred first, forming a charge-separated intermediate state, before the electron is transferred to complete the triplet exciton transfer. In the second mechanism the QD exciton is rapidly tapped at a surface state, followed by triplet transfer to the ligand.^{27,28}

To differentiate between the possible mechanisms, it is important to have a good understanding of the HOMO and LUMO levels of the ligand relative to the valence and conduction bands of the QD. We therefore turned to cyclic voltammetry to determine these, Fig. S6–S8 (ESI[†]). Interestingly the HOMO of the four ligands is very similar, Fig. 3, and the four ligands have equally poor alignment for hole-mediated triplet transfer. We also performed DFT calculations of the neutral and deprotonated ligands to corroborate our experimental findings, and estimate the triplet energy of all ligands, see the ESI[†] Fig. S9–S12 and Table S1 for details. The calculated frontier orbital energies for both the neutral and deprotonated ligands match well with the measured HOMO and LUMO levels. Only Tc-SH show any significant difference between the neutral and deprotonated form, where the HOMO–LUMO gap decreases as the HOMO rises in energy enough to open up for hole transfer from the QD, Fig. S9 (ESI[†]). However, as the Tc-SH ligand absorption spectrum when bound to the PbS QD is unchanged compared to the free form, we conclude that the neutral form is a better description of the bound ligand. Hence, both experimental and calculations indicate that hole transfer between PbS QDs and the bound ligands is improbable. It should be noted that the surface ligands can alter the valence and conduction bands of the QDs, which might open up for



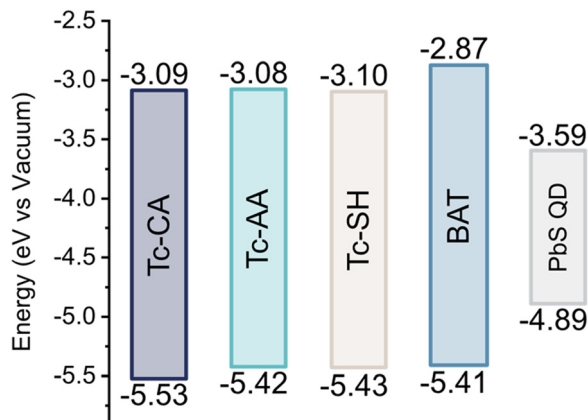


Fig. 3 HOMO and LUMO levels of the ligands and PbS/OA QDs. Determined from cyclic voltammetry relative to ferrocene.

possible hole transfer.³⁸ However, since the ligand loading of the active ligand is relatively small compared to the native oleic acid coverage, and that the ligands themselves are energetically similar, we assume that the influence of the tetracene ligands on the PbS conduction and valence bands is small enough for us to disregard this effect. Ruling out hole-transfer-mediated triplet transfer would suggest that the stepwise mechanism is governed by surface states on the QD. Triplet transfer to the BAT ligand on the other hand occurs *via* direct triplet transfer as concluded above. The estimated triplet energies are reported in Table S1 (ESI[†]). The calculated T_1 for Tc-CA is about 0.1 eV lower than that previously determined experimentally.²⁵ The triplet energies are similar between all ligands, with BAT having a 0.1 eV higher triplet energy, in accordance with the higher S_1 energy. Hence, the difference in energy of the ligand triplets is unlikely to explain the difference in mechanism between the ligands.

The Tang group has readily studied *peri*-substituted tetracene ligands similar to BAT (*e.g.* tetracene-5-carboxylic acid, 5CT).^{19,32,39,40} Interestingly, triplet transfer to 5CT and its derivatives have all been through direct Dexter transfer,^{32,39,40} whereas *pro-cata* substituted pentacenes have displayed stepwise triplet transfer.^{27,33} Tang and co-workers have determined the normalized rate of triplet transfer to 5CT from PbS as $\sim 2 \times 10^8 \text{ s}^{-1}$,⁴⁰ 3–4 orders of magnitude greater than that observed for the ligands here. These differences can be rationalized in the following ways. First, since PbS QDs are highly quantum confined, *peri*-substituted ligands like 5CT are expected to result in the strongest coupling.³⁷ Secondly, compared to the structurally similar BAT, 5CT is significantly closer to the QD surface as it lacks the phenyl-spacer. For example, 5CPT that also has a phenyl spacer has a normalized triplet transfer rate of $9 \times 10^5 \text{ s}^{-1}$,³² still greater than that for BAT, but significantly slower than 5CT. Thirdly, a trap state mediated triplet transfer as observed for Tc-CA, Tc-AA and Tc-SH, is expected to be significantly slower compared to direct transfer,⁴¹ as observed for 5CT.

What governs the change in mechanism is still unclear. Based on our findings and the results discussed above for other

acene ligands it seems that the binding geometry is the determining factor. Wu *et al.* observed that the binding geometry significantly influenced the coupling between QD and ligand,³⁷ however this is not sufficient to explain the change in mechanism observed here. Our current hypothesis is that the surface states are introduced during ligand exchange, and that the different binding geometries and local size of the ligand expels the native oleic acid ligands differently, resulting in trap states for the *pro-cata* substituted ligands, but not for *peri*-substituted ligands such as BAT and 5CT. These directions will be explored in future research.

Triplet–Triplet annihilation upconversion as a measure of triplet transfer efficiency

We continue our study by investigating the efficiency of triplet energy transfer in all four systems. Only 20% of the QD exciton population was quenched by BAT, whereas 100% of the QD population was quenched when the other three ligands were attached. That could suggest that Tc-CA, Tc-AA and Tc-SH are more efficient as triplet acceptors. We therefore used these PbS/ligand systems as sensitizers for NIR-to-visible photon upconversion based on triplet–triplet annihilation^{1,6,42–44} to get an indirect measure of the triplet yield.

In triplet–triplet annihilation upconversion a triplet sensitizer absorbs low-energy photons and subsequently transfers the triplet energy to an annihilator molecule. The triplet excited annihilator then interacts with another triplet excited annihilator to fuse the energy, forming a singlet excited annihilator and a ground state annihilator. The singlet excited annihilator can then emit a high-energy photon when returning to its ground state. The upconversion quantum yield (ϕ_{UC}), *i.e.* the number of photons emitted by the annihilator per absorbed photons by the sensitizer can be described by eqn (1):

$$\phi_{UC} = \phi_{TET-L} \phi_{TET-A} \phi_{TTA} \phi_F \quad (1)$$

where ϕ_{TET-L} is the triplet transfer efficiency from QD to ligand, ϕ_{TET-A} is the triplet transfer efficiency from ligand to annihilator, ϕ_{TTA} is the triplet–triplet annihilation quantum yield and ϕ_F is the fluorescence quantum yield of the annihilator.

By mixing the PbS/ligand sensitizers with rubrene, a common annihilator molecule, in deaerated toluene, upconverted yellow emission is observed upon excitation with a 785 nm CW laser for all PbS/ligand sensitizers. Interestingly, PbS/BAT outperformed the other three PbS/ligand sensitizers displaying 5 times greater upconversion emission intensity than the second best PbS/Tc-CA sensitizer, Fig. 4.

From eqn (1) it is understood that the observed upconversion intensity depends on the efficiency of a number of processes. As we use the same annihilator and concentration in the samples ϕ_F is the same across all samples. Furthermore, ϕ_{TTA} will depend on the concentration of rubrene triplets, which relates to the excitation power and the efficiency of the two



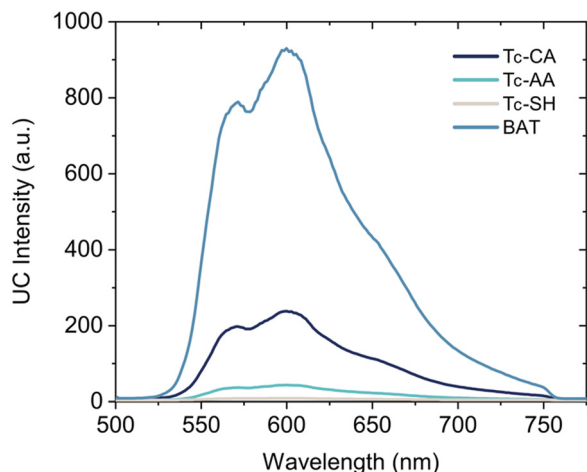


Fig. 4 Upconverted anti-Stokes emission upon 785 nm excitation of samples containing PbS/Ligand and 10 mM Rubrene in oxygen free toluene. Laser scatter is filtered by a 750 nm short pass filter.

triplet transfer processes.^{45,46} However, for a given triplet concentration, ϕ_{TTA} is an intrinsic property of the annihilator, hence a reduction in ϕ_{UC} due to a reduction in ϕ_{TTA} across the samples would be directly linked to the two triplet transfer processes. Hence, it remains to elucidate if the reduction in the overall triplet transfer originates from the triplet transfer from QD to ligand (TET-L), or from ligand to the annihilator rubrene (TET-A). The triplet transfer from ligand to rubrene is a bimolecular process which depends on both the rubrene concentration and triplet lifetime of the ligand. Assuming a bimolecular triplet transfer rate to rubrene of $\phi_{\text{TET-A}} = 1 \times 10^8 \text{ M}^{-1} \text{ s}^{-1}$, a reasonable rate considering triplet transfer to rubrene in similar systems,^{47,48} we can estimate the triplet transfer efficiency $\phi_{\text{TET-A}}$ from the ligand lifetime and rubrene concentration [Rub] according to eqn (2):

$$\phi_{\text{TET-A}} = 1 - \frac{1}{1 + k_{\text{TET-A}} \tau_{\text{Ligand}} [\text{Rub}]} \quad (2)$$

With the rubrene concentration at 10 mM the bimolecular triplet transfer efficiency to rubrene is estimated to be >95% for Tc-CA, Tc-AA and BAT, and ~75% for Tc-SH due to the shorter triplet lifetime (Table 1). In fact, for the more than 5 times lower upconversion intensity of the *pro-cata* anchored ligands to be explained by the reduction in diffusional triplet transfer the bimolecular rate constant, $k_{\text{TET-A}}$ for the *pro-cata* ligands must be as low as $10^5 \text{ M}^{-1} \text{ s}^{-1}$, see the ESI† for further details. For example, even for $k_{\text{TET-A}} = 0.4 \times 10^8 \text{ M}^{-1} \text{ s}^{-1}$ the triplet transfer efficiency to rubrene is >90% for all but Tc-SH. Based on these estimates, we conclude that the main reason for the difference in observed upconversion emission intensity stems directly from the difference in triplet transfer from QD to ligand, $\phi_{\text{TET-L}}$. Hence, the upconversion intensity is therefore a relative measure of the triplet population of the ligands. The difference in upconversion intensity in these PbS/ligand systems highlights an interesting finding in these PbS/ligand systems: more triplets are transferred to BAT than the other three

ligands, even though the transfer rate is slower. We can therefore conclude that the direct mechanism which governs triplet transfer in PbS/BAT does not introduce significant loss pathways, whereas a surface mediated mechanism, as in the cases for PbS/Tc-CA, PbS/Tc-AA and PbS/Tc-SH is plagued by parallel loss pathways competing with the triplet transfer.

Conclusions

In summary, we have studied the triplet transfer from PbS QDs to organic semiconductors in four QD/ligand systems where the ligand is a TIPS-tetracene derivative with either a carboxylic acid (Tc-CA), acetic acid (Tc-AA), methanethiol (Tc-SH) or benzoic acid (BAT) anchor group. We find that for the three first ligands, substituted on the short *pro-cata* side, triplet energy occurs through a stepwise mechanism. Based on the band alignment we rule out hole-mediated triplet transfer,^{14,15,33} which suggests a QD surface-state-mediated triplet transfer mechanism.^{27,28} In the PbS/BAT system, where the ligand is anchored *via* the long *peri* side, direct Dexter-like triplet energy transfer is observed. Considering the energetic similarities between all four ligands the major difference between the Tc-CA/Tc-AA/Tc-SH and BAT ligand is the binding geometry. How the binding geometry might influence the triplet transfer mechanism will be investigated in future work, but it might relate to previous observations of *peri* substitutions in pentacene having a greater impact on the electronic nature of the acene core compared to *pro-cata* substitution.⁴⁹ However, from triplet-triplet annihilation photon upconversion measurements we can conclude that the direct triplet transfer mechanism, even though slower, is more efficient, suggesting that the surface-mediated transfer is plagued with parasitic loss pathways. Therefore, materials with direct Dexter-like triplet transfer are preferred for high-efficiency applications.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We thank the Winton Programme for the Physics of Sustainability and the Engineering and Physical Sciences Research Council (Grant EP/P027741/1) for funding. This project has received funding from the European Research Council (ERC) under the European Union's Horizon 2020 research and innovation programme (grant agreement no. 758826). VG acknowledges funding from the Swedish research council, Vetenskapsrådet 2018-00238. J. R. A. acknowledges Cambridge Commonwealth European and International Trust for financial support. Z. Z. acknowledges funding from the European Union's Horizon 2020 research and innovation programme under the Marie Skłodowska-Curie Actions grant (no. 842271 – TRITON project). J. X. acknowledges EPSRC Cambridge NanoDTC, EP/L015978/1 for financial support. D. G. C. acknowledges the Herchel Smith fund



- Harvesting of Triplet Excitons Generated by Singlet Fission, *J. Am. Chem. Soc.*, 2019, **141**, 12907–12915, DOI: [10.1021/jacs.9b06584](https://doi.org/10.1021/jacs.9b06584).
- 25 V. Gray, J. R. Allardice, Z. Zhang, S. Dowland, J. Xiao, A. J. Petty, J. E. Anthony, N. C. Greenham and A. Rao, Direct vs Delayed Triplet Energy Transfer from Organic Semiconductors to Quantum Dots and Implications for Luminescent Harvesting of Triplet Excitons, *ACS Nano*, 2020, **14**, 4224–4234, DOI: [10.1021/acsnano.9b09339](https://doi.org/10.1021/acsnano.9b09339).
- 26 Y. Han, S. He, X. Luo, Y. Li, Z. Chen, W. Kang, X. Wang and K. Wu, Triplet Sensitization by “Self-Trapped” Excitons of Nontoxic CuInS₂ Nanocrystals for Efficient Photon Upconversion, *J. Am. Chem. Soc.*, 2019, **141**(33), 13033–13037, DOI: [10.1021/jacs.9b07033](https://doi.org/10.1021/jacs.9b07033).
- 27 J. A. Bender, E. K. Raulerson, X. Li, T. Goldzak, P. Xia, T. Van Voorhis, M. L. Tang and S. T. Roberts, Surface States Mediate Triplet Energy Transfer in Nanocrystal-Acene Composite Systems, *J. Am. Chem. Soc.*, 2018, **140**(24), 7543–7553, DOI: [10.1021/jacs.8b01966](https://doi.org/10.1021/jacs.8b01966).
- 28 C. M. Papa, S. Garakyaraghi, D. B. Granger, J. E. Anthony and F. N. Castellano, TIPS-Pentacene Triplet Exciton Generation on PbS Quantum Dots Results from Indirect Sensitization, *Chem. Sci.*, 2020, **11**, 5690–5696, DOI: [10.1039/D0SC00310G](https://doi.org/10.1039/D0SC00310G).
- 29 V. Gray, Z. Zhang, S. Dowland, J. R. Allardice, A. M. Alvertis, J. Xiao, N. C. Greenham, J. E. Anthony and A. Rao, Thiol-Anchored TIPS-Tetracene Ligands with Quantitative Triplet Energy Transfer to PbS Quantum Dots and Improved Thermal Stability, *J. Phys. Chem. Lett.*, 2020, **11**, 7239–7244, DOI: [10.1021/acs.jpcclett.0c02031](https://doi.org/10.1021/acs.jpcclett.0c02031).
- 30 X. Li, Z. Huang, R. Zavala and M. L. Tang, Distance-Dependent Triplet Energy Transfer between CdSe Nanocrystals and Surface Bound Anthracene, *J. Phys. Chem. Lett.*, 2016, **7**(11), 1955–1959, DOI: [10.1021/acs.jpcclett.6b00761](https://doi.org/10.1021/acs.jpcclett.6b00761).
- 31 Z. Huang, Z. Xu, T. Huang, V. Gray, K. Moth-Poulsen, T. Lian and M. L. Tang, Evolution from Tunneling to Hopping Mediated Triplet Energy Transfer from Quantum Dots to Molecules, *J. Am. Chem. Soc.*, 2020, **142**(41), 17581–17588, DOI: [10.1021/jacs.0c07727](https://doi.org/10.1021/jacs.0c07727).
- 32 Z. Xu, Z. Huang, C. Li, T. Huang, F. A. Evangelista, M. L. Tang and T. Lian, Tuning the Quantum Dot (QD)/Mediator Interface for Optimal Efficiency of QD-Sensitized Near-Infrared-to-Visible Photon Upconversion Systems, *ACS Appl. Mater. Interfaces*, 2020, **12**, 36558–36567, DOI: [10.1021/acsmi.0c10269](https://doi.org/10.1021/acsmi.0c10269).
- 33 S. Garakyaraghi, C. Mongin, D. B. Granger, J. E. Anthony and F. N. Castellano, Delayed Molecular Triplet Generation from Energized Lead Sulfide Quantum Dots, *J. Phys. Chem. Lett.*, 2017, **8**(7), 1458–1463, DOI: [10.1021/acs.jpcclett.7b00546](https://doi.org/10.1021/acs.jpcclett.7b00546).
- 34 D. M. Kroupa, D. H. Arias, J. L. Blackburn, G. M. Carroll, D. B. Granger, J. E. Anthony, M. C. Beard and J. C. Johnson, Control of Energy Flow Dynamics between Tetracene Ligands and PbS Quantum Dots by Size Tuning and Ligand Coverage, *Nano Lett.*, 2018, **18**(2), 865–873, DOI: [10.1021/acs.nanolett.7b04144](https://doi.org/10.1021/acs.nanolett.7b04144).
- 35 A. J. Morris-Cohen, M. T. Frederick, L. C. Cass and E. A. Weiss, Simultaneous Determination of the Adsorption Constant and the Photoinduced Electron Transfer Rate for a CdS Quantum Dot–Viologen Complex, *J. Am. Chem. Soc.*, 2011, **133**(26), 10146–10154, DOI: [10.1021/ja2010237](https://doi.org/10.1021/ja2010237).
- 36 L. Nienhaus, M. Wu, N. Geva, J. J. Shepherd, M. W. B. Wilson, V. Bulović, T. Van Voorhis, M. A. Baldo and M. G. Bawendi, Speed Limit for Triplet-Exciton Transfer in Solid-State PbS Nanocrystal-Sensitized Photon Upconversion, *ACS Nano*, 2017, **11**(8), 7848–7857, DOI: [10.1021/acsnano.7b02024](https://doi.org/10.1021/acsnano.7b02024).
- 37 S. He, R. Lai, Q. Jiang, Y. Han, X. Luo, Y. Tian, X. Liu and K. Wu, Engineering Sensitized Photon Upconversion Efficiency via Nanocrystal Wavefunction and Molecular Geometry, *Angew. Chem., Int. Ed.*, 2020, **59**(40), 17726–17731, DOI: [10.1002/anie.202009066](https://doi.org/10.1002/anie.202009066).
- 38 P. R. Brown, D. Kim, R. R. Lunt, N. Zhao, M. G. Bawendi, J. C. Grossman and V. Bulović, Energy Level Modification in Lead Sulfide Quantum Dot Thin Films through Ligand Exchange, *ACS Nano*, 2014, **8**(6), 5863–5872, DOI: [10.1021/nn500897c](https://doi.org/10.1021/nn500897c).
- 39 Z. Huang, Z. Xu, M. Mahboub, X. Li, J. W. Taylor, W. H. Harman, T. Lian and M. L. Tang, PbS/CdS Core–Shell Quantum Dots Suppress Charge Transfer and Enhance Triplet Transfer, *Angew. Chem., Int. Ed.*, 2017, **56**(52), 16583–16587, DOI: [10.1002/anie.201710224](https://doi.org/10.1002/anie.201710224).
- 40 Z. Huang, Z. Xu, M. Mahboub, Z. Liang, P. Jaimes, P. Xia, K. R. Graham, M. L. Tang and T. Lian, Enhanced Near-Infrared-to-Visible Upconversion by Synthetic Control of PbS Nanocrystal Triplet Photosensitizers, *J. Am. Chem. Soc.*, 2019, **141**(25), 9769–9772, DOI: [10.1021/jacs.9b03385](https://doi.org/10.1021/jacs.9b03385).
- 41 T. Jin and T. Lian, Trap State Mediated Triplet Energy Transfer from CdSe Quantum Dots to Molecular Acceptors, *J. Chem. Phys.*, 2020, **153**(7), 074703, DOI: [10.1063/5.0022061](https://doi.org/10.1063/5.0022061).
- 42 V. Gray, D. Dzebo, M. Abrahamsson, B. Albinsson and K. Moth-Poulsen, Triplet–Triplet Annihilation Photon-Upconversion: Towards Solar Energy Applications, *Phys. Chem. Chem. Phys.*, 2014, **16**(22), 10345–10352, DOI: [10.1039/C4CP00744A](https://doi.org/10.1039/C4CP00744A).
- 43 N. Yanai and N. Kimizuka, New Triplet Sensitization Routes for Photon Upconversion: Thermally Activated Delayed Fluorescence Molecules, Inorganic Nanocrystals, and Singlet-to-Triplet Absorption, *Acc. Chem. Res.*, 2017, **50**(10), 2487–2495, DOI: [10.1021/acs.accounts.7b00235](https://doi.org/10.1021/acs.accounts.7b00235).
- 44 V. Gray, K. Moth-Poulsen, B. Albinsson and M. Abrahamsson, Towards Efficient Solid-State Triplet–Triplet Annihilation Based Photon Upconversion: Supramolecular, Macromolecular and Self-Assembled Systems, *Coord. Chem. Rev.*, 2018, **362**, 54–71, DOI: [10.1016/j.ccr.2018.02.011](https://doi.org/10.1016/j.ccr.2018.02.011).
- 45 A. Haeefele, J. Blumhoff, R. S. Khnayzer and F. N. Castellano, Getting to the (Square) Root of the Problem: How to Make Noncoherent Pumped Upconversion Linear, *J. Phys. Chem. Lett.*, 2012, **3**(3), 299–303, DOI: [10.1021/jz300012u](https://doi.org/10.1021/jz300012u).
- 46 S. Hoseinkhani, R. Tubino, F. Meinardi and A. Monguzzi, Achieving the Photon Up-Conversion Thermodynamic Yield Upper Limit by Sensitized Triplet–Triplet Annihilation, *Phys. Chem. Chem. Phys.*, 2015, **17**(6), 4020–4024, DOI: [10.1039/C4CP03936J](https://doi.org/10.1039/C4CP03936J).



- 47 Y. Y. Cheng, B. Fückel, T. Khoury, R. G. C. R. Clady, M. J. Y. Tayebjee, N. J. Ekins-Daukes, M. J. Crossley and T. W. Schmidt, Kinetic Analysis of Photochemical Upconversion by Triplet-Triplet Annihilation: Beyond Any Spin Statistical Limit, *J. Phys. Chem. Lett.*, 2010, **1**(12), 1795–1799, DOI: [10.1021/jz100566u](https://doi.org/10.1021/jz100566u).
- 48 T. W. Schmidt and F. N. Castellano, Photochemical Upconversion: The Primacy of Kinetics, *J. Phys. Chem. Lett.*, 2014, **5**(22), 4062–4072, DOI: [10.1021/jz501799m](https://doi.org/10.1021/jz501799m).
- 49 B. Milián Medina, J. E. Anthony and J. Gierschner, Independent Tuning of Electronic Levels in Pentacene by Site-Specific Substitution, *Chem. Phys. Chem.*, 2008, **9**(11), 1519–1523, DOI: [10.1002/cphc.200800122](https://doi.org/10.1002/cphc.200800122).

