

## RESEARCH ARTICLE

View Article Online  
View Journal | View IssueCite this: *Inorg. Chem. Front.*, 2024,  
11, 2876

## A chelating coordination modulation method for the synthesis of Ti-MOF single crystals†

Hui-Zi Li,<sup>a,b</sup> Shangda Li,<sup>a</sup> Fei Wang<sup>a</sup> and Jian Zhang<sup>a</sup>

Even though titanium-based metal–organic frameworks (Ti-MOFs) are promising as efficient photocatalysts, the high reactivity of titanium ions makes the synthesis and structure determination of new Ti-MOFs quite challenging. In this study, we propose a chelating coordination modulation (CCM) method for the synthesis of Ti-MOF single crystals by using molecules with chelating coordination groups as the modulator. Thanks to this method, three Ti-MOFs (FIR-117–119) have been obtained and their structures were determined by single crystal X-ray diffraction (SCXRD), validating the universality of this approach. By capturing the intermediate and determining its single crystal structure, the role of the modulator in the growth of Ti-MOF single crystals is clarified: the use of a chelating coordination molecule as the modulator and a competitive ligand slows down the reaction rate by forming Ti–modulator key intermediates, which balance the formation of Ti-MOFs and growth of single crystals. Furthermore, FIR-119 exhibits excellent photocatalytic performance under visible light due to its good light absorption ability with a narrow bandgap. These results highlight the potential of the chelating coordination modulation method in the synthesis of new photoactive Ti-MOFs and their single crystals.

Received 17th February 2024,  
Accepted 15th April 2024

DOI: 10.1039/d4qi00436a

rsc.li/frontiers-inorganic

## Introduction

Metal–organic frameworks (MOFs) have been extensively researched for gas separation and storage owing to their unique pore structure and high surface areas.<sup>1–7</sup> Recently, they have emerged as promising photocatalysts that combine the merits of molecular catalysts and heterogeneous systems, showing potential as alternatives to traditional photocatalysts like TiO<sub>2</sub>.<sup>8</sup> Among MOFs, titanium-based metal–organic frameworks (Ti-MOFs) have garnered special attention due to their excellent photocatalytic activity.<sup>9–21</sup> Nevertheless, the scarcity of Ti-MOFs has limited the research in this area, with the focus mainly on two Ti-MOFs (MIL-125 and MIL-125-NH<sub>2</sub>) reported over ten years ago.<sup>22–24</sup> Therefore, there is an urgent need to synthesize new Ti-MOFs.

The main challenge in synthesizing new Ti-MOFs lies in the high activity and uncontrollable reactivity of Ti<sup>4+</sup> ions,<sup>25</sup> which lead to the formation of various byproducts, including TiO<sub>2</sub>,

titanium-oxo clusters (TOCs),<sup>26,27</sup> and even unidentified species. The mixing of different species in most cases presents significant difficulties in structure determination and performance study. Regarding the structure determination of compounds, powder XRD combined with theoretical calculations can be employed for pure-phase Ti-MOFs,<sup>14,16,28–32</sup> whereas it becomes ineffective for mixed phases containing different species. Another method, namely the electron diffraction method using a cryo-electron microscope can also be used to determine the structure of some micro- and nano-sized microcrystalline Ti-MOFs.<sup>33,34</sup> However, it should be noted that most MOFs are unstable under electron beam irradiation, making the application of this method very demanding for materials.<sup>35</sup> Additionally, this instrument is expensive and not widely available. In comparison, single crystal XRD analysis remains the most popular and universal method used to determine the structure of substances at present. It is well-known that synthesizing single crystals is an important means to separate and purify different substances. Therefore, the synthesis of Ti-MOF single crystals not only allows for easy determination of the structure *via* single crystal XRD, but also realizes the separation and purification of Ti-MOFs, which is of great significance in research and practical applications. However, the uncontrollable reaction kinetics leads to a mismatch between the formation of Ti-MOFs and the growth of single crystals, making the synthesis of Ti-MOFs suitable for single crystal XRD measurement more challenging.

<sup>a</sup>State Key Laboratory of Structural Chemistry, Fujian Institute of Research on the Structure of Matter, Chinese Academy of Sciences, Fuzhou, Fujian 350002, P. R. China. E-mail: wangfei04@fjirsm.ac.cn; zhj@fjirsm.ac.cn

<sup>b</sup>University of Chinese Academy of Sciences, Beijing 100049, P. R. China

†Electronic supplementary information (ESI) available. CCDC 2287493 (FIR-117), 2287494 (FIR-118) and 2287495 (FIR-119). For ESI and crystallographic data in CIF or other electronic format see DOI: <https://doi.org/10.1039/d4qi00436a>

In 2014, Zhang and coworkers<sup>36</sup> synthesized Ti-MOF (NTU-9) single crystals based on the 2,5-dihydroxyterephthalic acid (H<sub>4</sub>DOBDC) ligand by using acetic acid as the solvent. While Serre's group synthesized the intergrown crystals of MIL-167 from the same reactants in a diethylformamide (DEF)/methanol mixed solvent.<sup>37</sup> Subsequently, Marti-Gastaldo constructed a Ti-MOF (MUV-11) in a dimethylformamide(DMF)/acetic acid mixed solvent using a chelating ligand, 1,4-phenylhydroxamic acid (*p*-H<sub>2</sub>bhdh).<sup>38</sup> These results suggest that monocarboxylic acids like acetic acid may play the role of a modulator in the formation of Ti-MOF single crystals, similar to that in the coordination modulation method of zirconium-based MOFs (Zr-MOFs).<sup>39</sup> In 2015, Zhou and coworkers<sup>40</sup> further developed this method for the synthesis of Ti-MOFs. The reaction of the hexameric titanium-oxo cluster precursor (Ti<sub>6</sub>) and the porphyrin carboxylic acid (TCPP) ligand with benzoic acid as a modulator gave single crystals of PCN-22. PCN-22 contained a new Ti<sub>7</sub> cluster which was supposed to be rearranged from the original Ti<sub>6</sub> cluster. Subsequently, using similar methods, different research groups successively synthesized single crystals of several Ti-MOFs, such as Ti-TBP,<sup>41</sup> Ti<sub>3</sub>-BPDC,<sup>42</sup> DGIST-1,<sup>43</sup> and FIR-125.<sup>17</sup> However, the successful examples based on this method are extremely limited, and the influence of the modulator on single crystal formation is poorly understood. In addition, compared with the original titanium-oxo cluster precursor, the Ti-based secondary building units (SBUs) in these Ti-MOFs changed without exception.<sup>44</sup> This change highlights the uncontrollability of this Ti-MOF synthesis method and emphasizes the importance of developing new alternative synthesis strategies.

In this work, we propose a chelating coordination modulation (CCM) method for the synthesis of Ti-MOF single crystals. Inspired by the syntheses of NTU-9 and MIL-167, we chose the self-assembly of Ti and 2,5-dihydroxyterephthalic acid (H<sub>4</sub>DOBDC) as the model system and employed various molecules with chelating coordination groups as modulators. Thanks to this method, we successfully obtained three Ti-MOFs, namely FIR-117, FIR-118, and FIR-119 (FIR = Fujian Institute Research), and their structures were determined using single crystal X-ray diffraction (SCXRD). By capturing the intermediate and determining its single crystal structure, we clarify the role of the modulator in the growth of Ti-MOF single crystals. Initially, the four coordinated alcohols on Ti (iOPr)<sub>4</sub> are replaced by three modulators in the form of chelation coordination, transforming the unstable tetrahedral configuration of the Ti center into a stable octahedral configuration. Subsequently, the coordinated modulator is replaced by bridging ligands to form a framework. The core aspect of this method lies in using chelating coordination molecules as the modulator and a competitive ligand, which slows down the reaction rate by forming Ti-modulator intermediates, thereby achieving a balance between the formation of Ti-MOFs and growth of single crystals. Furthermore, FIR-119 exhibits excellent photocatalytic performance under visible light due to its good light absorption ability with a narrow bandgap.

## Results and discussion


NTU-9 is a typical mononuclear Ti-MOF with a 2D honeycomb-type (hcb) layer.<sup>36</sup> The single crystal structural analysis of NTU-9 reveals that a chelating ligand (L) such as DODBC tends to chelate with Ti ions to form a mononuclear TiL<sub>3</sub> subunit (SBU). In comparison with Ti-MOFs based on Ti-oxo cluster SBUs, its simple coordination mode provides certain advantages in the rational design and prediction of the structure of Ti-MOFs. In addition, this coordination mode also inhibits the excessive hydrolysis of Ti<sup>4+</sup> ions, which could otherwise form complex titanium oxide clusters and other by-products. But things are not that simple. Serre and coworkers synthesized a 3D Ti-MOF (MIL-167) with a similar coordination mode and linkage, using the same reactants but only changing the solvent to diethylformamide (DEF) instead of acetic acid.<sup>37</sup> The as-synthesized MIL-167 formed intergrown crystallites with a large crystal size, which prevented its structure determination by SCXRD. As a result, its structure was determined using the PXRD method.

Based on the above analysis, we chose Ti(O<sup>i</sup>Pr)<sub>4</sub> as the Ti source and H<sub>4</sub>DOBDC as the ligand to explore the feasibility of synthesizing new Ti-MOF single crystals. The initial attempt using DEF and acetic acid as a mixed solvent resulted in the formation of intergrown crystals of MIL-167. Therefore, it is speculated that the reaction speed is too fast, which is not conducive to the growth of single crystals. Considering the strong chelating coordination ability of the DOBDC ligand, we further introduced molecules with chelating coordination groups as modulators and competitive ligands. The results showed that the addition of the modulator effectively improved the crystallinity of the Ti-MOF.

High-quality Ti-MOF single crystals of FIR-117 and FIR-118 were synthesized using salicylic acid and squaric acid as modulators, respectively (details in the Synthesis section). SCXRD analyses reveal that both FIR-117 and FIR-118 crystallize in the triclinic *P* $\bar{1}$  space group but have different unit cell parameters (Table S1<sup>†</sup>). In both compounds, the Ti center is octahedrally coordinated by three different DOBDC ligands in the chelating mode (Fig. S1a<sup>†</sup>). Taking FIR-117 as an example, the bond length between Ti and the phenolic hydroxyl group O (denoted as O<sub>Ar</sub>) is approximately 1.87 Å while the bond length between Ti and the carboxylate group O (denoted as O<sub>CO<sub>2</sub></sub>) is ~2.01 Å, both of which are close to those of NTU-9 and other reported TOCs.<sup>45</sup>

All the DOBDC ligands act as bridging ligands, while two types of ligands link Ti atoms to form an S-shaped 1D chain, which is then connected by the third ligand to form a wave-like 2D layer with a twisted hcb topology (Fig. 1a) in FIR-117. In comparison, in FIR-118, two kinds of DOBDC ligands link Ti atoms to form a zigzag 1D chain, which is connected by the third one to form a coplanar 2D layer with a twisted hcb topology (Fig. 1b).

These wave-like layers in FIR-117 stack in an AA manner along the *a*-axis. [NH<sub>2</sub>(C<sub>2</sub>H<sub>5</sub>)<sub>2</sub>]<sup>+</sup> cations from the decomposition of DEF act as counterions and are located between these

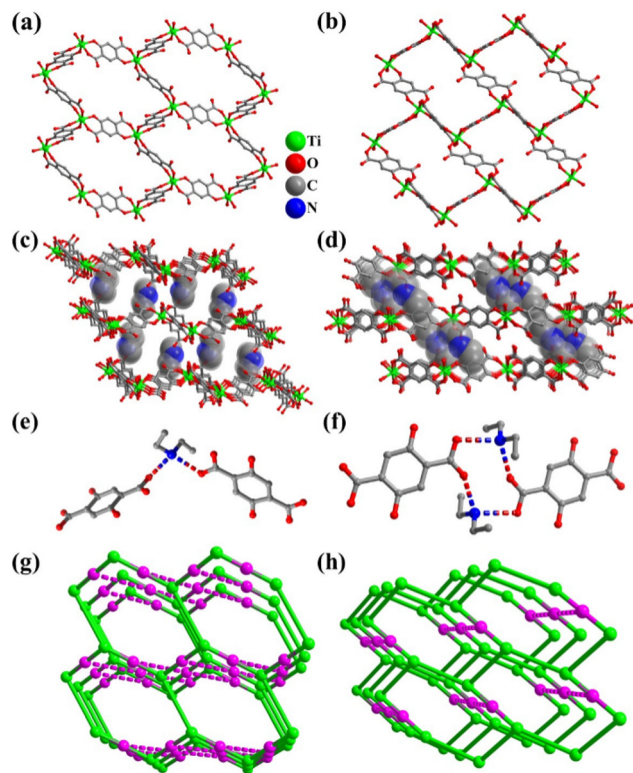

**Fig. 1** The structural comparison between FIR-117 and FIR-118. (a) View of the wave-like 2D layer of FIR-117 along the *a*-axis; (b) view of the coplanar 2D layer of FIR-118 along the *a*-axis; (c) view of the packing mode of the layers along the *c*-axis in FIR-117; (d) view of the packing mode of the layers along the *c*-axis in FIR-118; (e) the hydrogen-bond interactions between the  $[\text{NH}_2(\text{C}_2\text{H}_5)_2]^+$  cations and DOBDC ligands in FIR-117; (f) the hydrogen-bond interactions between the  $[\text{NH}_2(\text{C}_2\text{H}_5)_2]^+$  cations and DOBDC ligands in FIR-118; (g) the simplified 3,4-connected tfo topology of FIR-117; (h) the simplified 3,4-connected tfc topology of FIR-118.

layers (Fig. 1c). One  $[\text{NH}_2(\text{C}_2\text{H}_5)_2]^+$  cation links two DOBDC ligands of two adjacent layers through strong hydrogen bond interactions ( $\text{N}\cdots\text{O}$  distances are 2.720 and 2.849 Å) (Fig. 1e and S1b<sup>†</sup>). Therefore, adjacent layers are connected by  $[\text{NH}_2(\text{C}_2\text{H}_5)_2]^+$  cations to form a 3D hydrogen-bonded framework. As for FIR-118, the coplanar layers are also stacked in an AA manner along the *a*-axis, and the space between these layers is filled by  $[\text{NH}_2(\text{C}_2\text{H}_5)_2]^+$  cations (Fig. 1d). In FIR-118, two  $[\text{NH}_2(\text{C}_2\text{H}_5)_2]^+$  cations link two DOBDC ligands of two adjacent layers through strong hydrogen bond interactions ( $\text{N}\cdots\text{O}$  distances are 2.720 and 2.849 Å) (Fig. 1f and S1e<sup>†</sup>). The presence of multiple hydrogen bond interactions in FIR-118 is expected to endow it with good stability.

To better compare these two hydrogen-bonded frameworks, topological analysis was performed. In FIR-117, the DOBDC ligands with H-bond interactions act as 4-connected nodes, while others serve as linkers. Each Ti atom can be considered a 3-connected node (Fig. S1b and S1c<sup>†</sup>). The entire framework can be simplified as a 3,4-connected tfo topology (Fig. 1g). Similarly, the framework of FIR-118 can be simplified as a 3,4-

connected tfc topology (Fig. 1h and S1e<sup>†</sup>). The topological results clearly showed that the coplanar layers vertically connect ligands (dashed pink line) through hydrogen bonds to form a 3D network of FIR-118, while the wave-like layer connected ligands by staggered hydrogen bonds to form a 3D network of FIR-117.

Encouraged by these results, we expanded our investigation to explore the feasibility of using other organic compounds containing chelating groups as modulators. In addition to the above-mentioned salicylic acid and squaric acid, we further examined other compounds containing O, O' chelating groups, S, O chelating groups, and N, O chelating groups. The results showed that these alternative compounds can also be utilized as modulators to successfully synthesize Ti-MOF single crystals. The specific experimental results are summarized in Table 1.

In particular, by using thiosalicylic acid as a modulator, we successfully synthesized single crystals of FIR-119. SCXRD analysis reveals that FIR-119 crystallized in the cubic  $I\bar{4}3d$  space group (Table S1<sup>†</sup>) and is isostructural to MIL-167. However, its volume is *ca.* 13.5% smaller than that of MIL-167.

In FIR-119, each Ti center is also octahedrally coordinated by three different DOBDC ligands in a chelating mode. The  $\text{Ti}-\text{O}_{\text{Ar}}$  and  $\text{Ti}-\text{O}_{\text{CO}_2}$  bond lengths are 1.88 and 1.98 Å (Table S2<sup>†</sup>), falling within a reasonable range. Three DOBDC ligands coordinate with one Ti center to form a fan-type  $\text{Ti}(\text{DOBDC})_3$  unit and two chiral  $\text{Ti}(\text{DOBDC})_3$  units with  $\Lambda$  (Fig. 2a) and  $\Delta$  (Fig. 2b) configurations coexisting in the same structure. A pair of  $\Delta$  and  $\Lambda$  units are slightly staggered along the same direction (Fig. 2c and d). The  $\text{Ti}\cdots\text{Ti}$  distance between adjacent units is 9.45 Å, which is larger than the  $\text{Ti}\cdots\text{Ti}$  distances connected by DOBDC ligands (8.46 Å).


In FIR-119, all  $\Lambda$ - $\text{Ti}(\text{DOBDC})_3$  units link each other to form a 3D framework (Fig. 2e) with a chiral srs topology (Fig. 2f). Similarly, all  $\Delta$ - $\text{Ti}(\text{DOBDC})_3$  units connect with each other to form the opposite chiral 3D framework. The interpenetration (2-fold) of opposite chiral frameworks results in the crystallization in the nonchiral space group. It is deduced that the disordered  $[\text{NH}_2(\text{C}_2\text{H}_5)_2]^+$  cations decomposed from DEF serve as counterions to balance the charge. This deduction is further supported by  $^1\text{H}$  NMR and  $^{13}\text{C}$  NMR results (Fig. S2 and S3<sup>†</sup>).

From the above discussion, it can be seen that the successful syntheses of FIR-117–119 single crystals benefit from the

**Table 1** Ti-MOF single-crystals synthesized using different modulators

Modulator	Ti-MOF
	FIR-117
	FIR-118
	FIR-119



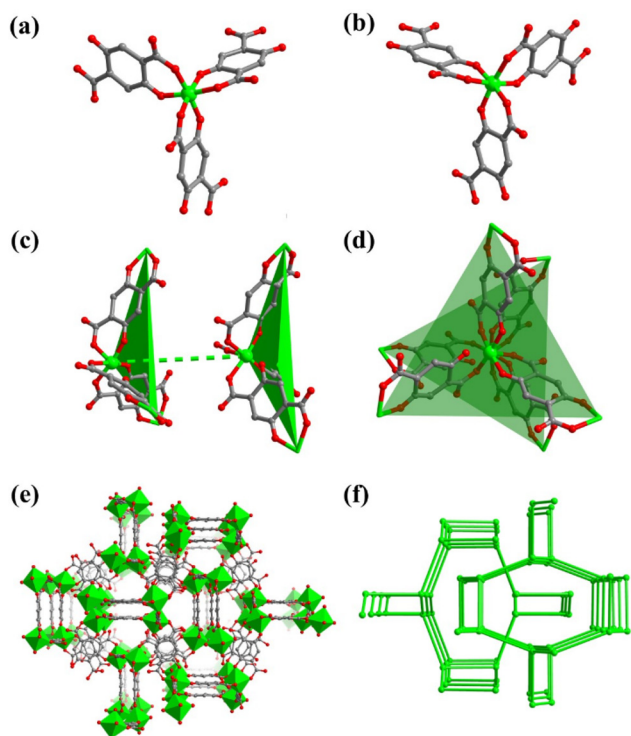


**Fig. 2** The chiral  $\text{Ti}(\text{DOBDC})_3$  units with  $\Lambda$  (a) and  $\Delta$  configurations (b) in FIR-119; a pair of  $\Delta$  and  $\Lambda$  units slightly staggered (c) along the same direction (d), with the  $\text{Ti}\cdots\text{Ti}$  distance (9.45 Å) marked with a dashed green line; (e) the interpenetrated 3D framework of FIR-119; (f) the simplified 2-fold interpenetrated srs topology.

addition of compounds with chelating coordination groups. Previous reports have indicated that introducing proline as a modulator helps to improve the quality of Zr-MOF single crystals.<sup>46</sup> In a series of comparative experiments, it was observed that both the carboxyl group and the *N*-heteroatom play important roles in the synthesis of Zr-MOF single crystals, but the specific roles are not yet clear.

Therefore, in order to clarify the roles of the modulators, we conducted comparative experiments. Previous experiments demonstrated that FIR-117 was obtained through a one-pot reaction of  $\text{Ti}(\text{OiPr})_4$ , salicylic acid and  $\text{H}_4\text{DOBDC}$ . Interestingly, when the reaction time was shortened or the temperature was lowered, a  $\text{Ti}(\text{salicylate})_3$  complex was obtained, suggesting that the  $\text{Ti}(\text{salicylate})_3$  complex may serve as an intermediate in the formation of FIR-117. Additionally, the reaction of  $\text{Ti}(\text{OiPr})_4$  with salicylic acid in the absence of  $\text{H}_4\text{DOBDC}$  also resulted in the formation of the  $\text{Ti}(\text{salicylate})_3$  complex. Furthermore, using the  $\text{Ti}(\text{salicylate})_3$  complex as the Ti source and reacting it with the DOBDC ligand, FIR-117 single crystals could also be obtained. Therefore, we deduced that the  $\text{Ti}(\text{salicylate})_3$  complex was the intermediate involved in the synthesis of FIR-117.

Based on these results, we propose a possible mechanism for the chelating coordination modulation (CCM) method to synthesize Ti-MOF single crystals (Fig. 3). First, in the presence

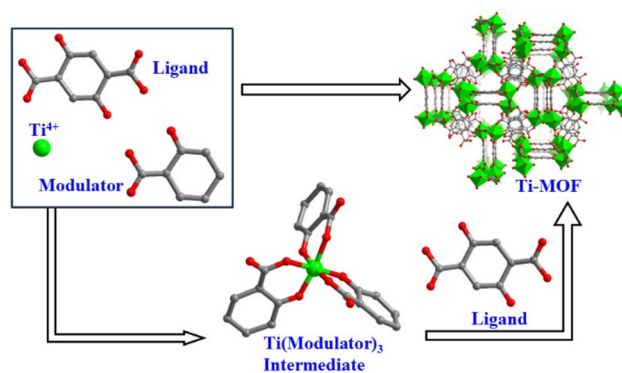


**Fig. 3** Possible mechanism of the chelating coordination modulation (CCM) method to synthesize Ti-MOF single crystals.

of a large amount of chelating coordination modulators, tetrahedrally coordinated  $\text{Ti}(\text{OiPr})_4$  with high reactivity reacts rapidly with modulators to form a more stable  $\text{Ti}(\text{modulator})_3$  intermediate. The formation of these  $\text{Ti}(\text{modulator})_3$  intermediates helps to inhibit the excessive hydrolysis of  $\text{Ti}^{4+}$  ions. Subsequently, DOBDC ligands with a similar coordination ability gradually replace the modulators on Ti in a controllable manner to form the final framework. The controllability is mainly reflected in the relatively reversible substitution reaction between the DOBDC ligand and the modulator, which slows down the formation of the framework and matches the growth speed of single crystals, thus realizing the synthesis of high-quality Ti-MOF single crystals.

The outcomes of our study illustrate that the chelating coordination modulation (CCM) method proves to be a highly effective approach for synthesizing single crystals of Ti-MOFs. The key aspect of the CCM method involves the use of molecules with chelating coordination groups as modulators, which play a crucial role in controlling the crystal growth process. Through the application of this method, we successfully synthesized high-quality Ti-MOF single crystals (FIR-117–119) and determined their structures using single crystal X-ray diffraction (SCXRD). The significance of the modulators in the growth of Ti-MOF single crystals was elucidated by capturing the intermediate species and determining their single crystal structures. Specifically, the modulators form stable mononuclear structures through chelating coordination with titanium ions, effectively inhibiting unwanted side reactions. This controllability ensures the successful synthesis of Ti-MOFs with desired structures and large-size single crystal growth. Our findings demonstrated the broad applicability of the CCM approach in synthesizing Ti-MOF single crystals with diverse structures and properties. This versatility opens up new possibilities for tailoring the properties of Ti-MOFs to suit specific applications. With the successful synthesis of Ti-MOF single crystals using various modulators, we anticipate that the CCM method holds promise for the rational design and synthesis of other metal–organic frameworks.

The powder XRD (PXRD) pattern of the as-synthesized crystal samples shows that most of the main peaks are well

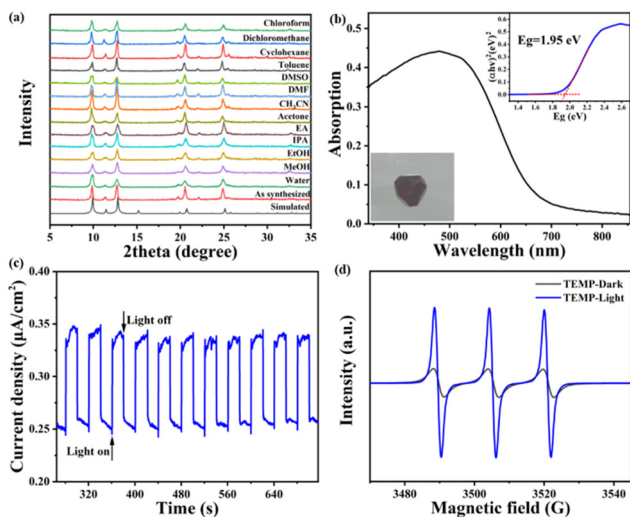

**Fig. 4** (a) Powder XRD patterns of FIR-119 treated with different solvents for 24 h. (b) UV-vis diffuse reflectance spectra of FIR-119 (Tauc plot of FIR-119 derived from UV-Vis diffuse reflectance spectra). (c) Photocurrent of FIR-119 under visible light periodic illumination ( $\lambda > 420$  nm). (d) EPR spectrum of FIR-119 in DMSO under visible light irradiation with a Xe lamp with TEMPO as the trapping agent.

consistent with the simulated patterns derived from SCXRD data, which confirmed the phase purity of FIR-117, FIR-118 and FIR-119 (Fig. S5, S6† and 4a). The thermogravimetric analysis results of FIR-117 and FIR-118 showed structural stability below 200 °C (Fig. S7 and S8†). Meanwhile, thermogravimetric analysis showed that the framework of FIR-119 can be stable at approximately 300 °C (Fig. S9†). Additionally, the solvent stability of FIR-119 was also evaluated. Powder XRD measurements demonstrated that FIR-119 remained stable after soaking in common solvents such as water, various alcohols, ethyl acetate (EA), acetonitrile ( $\text{CH}_3\text{CN}$ ), amides, toluene, dichloromethane and chloroform at room temperature for 24 hours (Fig. 4a). Compared to that of the DOBDC ligand, the diffuse reflectance UV-Vis spectrum of FIR-117, 118 and 119 showed a broad absorption band in the visible light range. The calculated bandgaps of DOBDC and FIR-117–119 from the Tauc plot are 2.67, 1.90, 1.86 and 1.95 eV (Fig. 4b, S10, S11 and S12†). FIR-117–119 show a lower bandgap mainly due to ligand-to-metal charge transfer (LMCT) from the DOBDC ligand to high-valence titanium ions. The photocurrent profile of FIR-119 indicates that it is photoactive under visible light illumination ( $\lambda > 420$  nm, Fig. 4c). The EDS spectrum and XPS spectrum of FIR-119 (Fig. S13 and S14a†) further confirm the presence of the elements titanium (Ti), nitrogen (N), oxygen (O), and carbon (C). The XPS Ti 2p region of FIR-119 shows two peaks with binding energies of 458.91 eV (Ti 2p<sub>3/2</sub>) and 464.71 eV (Ti 2p<sub>1/2</sub>), respectively, confirming that the valence state of Ti is +4 (Fig. S14b†). The electron paramagnetic resonance (EPR) test results showed that FIR-119 can produce  $^1\text{O}_2$  under visible light irradiation with 4-oxo-2,2,6,6-tetramethyl-1-piperidinyloxy (TEMPO) as the trapping agent (Fig. 4d). Therefore, FIR-119

**Table 2** Photocatalytic results of FIR-119 for aerobic CDC reactions under different conditions<sup>a</sup>

Entry	Catalyst	Light source	Yield
1	None	Visible light ( $\lambda > 420$ nm)	Trace
2	FIR-119	Without light	Trace
3	FIR-119	Visible light ( $\lambda > 420$ nm)	41%

<sup>a</sup> Reaction conditions: substrate A (0.2 mmol), diethyl phosphite B (0.24 mmol), and catalyst FIR-119 (10 mg) in 2 mL DMSO exposed to air under different conditions (light source and catalyst) at room temperature for 24 h.

should be a very promising photocatalyst, especially in the area of aerobic catalytic reactions.

Due to its excellent stability, effective visible light absorption capability, and notable photoactivity, this mononuclear Ti-MOF is anticipated to emerge as a novel type of visible light catalyst. The cross-dehydrogenation coupling (CDC) reaction, facilitated by visible light, represents a strategy for directly activating C–H bonds and establishing C–C bonds from uncomplicated compounds.<sup>47</sup> This reaction harnesses renewable energy, obviating the need for pre-functionalization of reactants, thereby synergistically promoting a green synthesis pathway. Consequently, we selected a representative aerobic CDC reaction involving *N*-phenyltetrahydroisoquinolines (A) and diethyl phosphite (B) to investigate the photocatalytic efficacy of FIR-119 (Table 2). When FIR-119 serves as a catalyst under visible light irradiation, the reaction yields 41% of product C (entry 3, Table 2 and Fig. S15†). The experimental findings further confirm FIR-119's commendable visible light and catalytic activity in CDC reactions. After 24 hours of CDC reaction, PXRD results (Fig. S16†) validate FIR-119's robust stability. As shown in Table 2, control experiments underscore the indispensability of both light and MOF photocatalysts in this typical CDC reaction. Under visible light conditions, devoid of a catalyst, product formation is nearly imperceptible. Likewise, in the absence of the FIR-119 catalyst, no product formation is observed under dark conditions (entry 2, Table 2).

## Conclusions

In conclusion, we have developed the chelating coordination modulation (CCM) method, employing molecules with chelating coordination groups as modulators, for the synthesis of Ti-MOFs. Our study showcases the versatility and effectiveness of the chelating coordination modulation method as a controlled synthesis tool for obtaining high-quality Ti-MOF single crystals with tailored properties. The insights gained from this research can pave the way for the development of novel functional materials and advanced catalysts for various appli-

cations, including in the field of visible light photocatalysis and beyond.

## Author contributions

Hui-Zi Li: synthesis, characterization, data curation, formal analysis, investigation, visualization, methodology and writing – original draft. Shangda Li: data curation and investigation. Fei Wang: conceptualization, data curation, formal analysis, investigation, writing – original draft, writing – review and editing, and funding acquisition. Jian Zhang: conceptualization, methodology, supervision, project administration and funding acquisition.

## Conflicts of interest

The authors declare no competing financial interest.

## Acknowledgements

This work was supported by the National Natural Science Foundation of China (21935010) and the Natural Science Foundation of Fujian Province (2022J01505).

## References

- 1 Y. Su, K. I. Otake, J. J. Zheng, S. Horike, S. Kitagawa and C. Gu, Separating water isotopologues using diffusion-regulatory porous materials, *Nature*, 2022, **611**, 289–294.
- 2 J. Wang, Y. Zhang, Y. Su, X. Liu, P. Zhang, R.-B. Lin, S. Chen, Q. Deng, Z. Zeng, S. Deng and B. Chen, Fine pore engineering in a series of isoreticular metal-organic frameworks for efficient C<sub>2</sub>H<sub>2</sub>/CO<sub>2</sub> separation, *Nat. Commun.*, 2022, **13**, 200.
- 3 H. Lin, Y. Yang, Y.-C. Hsu, J. Zhang, C. Welton, I. Afolabi, M. Loo and H.-C. Zhou, Metal-Organic Frameworks for Water Harvesting and Concurrent Carbon Capture: A Review for Hygroscopic Materials, *Adv. Mater.*, 2023, **36**, 2209073.
- 4 Q. Yan, J. Wang, L. Zhang, J. Liu, M. Wahiduzzaman, N. Yan, L. Yu, R. Dupuis, H. Wang, G. Maurin, M. Hirscher, P. Guo, S. Wang and J. Du, A squarate-pillared titanium oxide quantum sieve towards practical hydrogen isotope separation, *Nat. Commun.*, 2023, **14**, 4189.
- 5 L. Yu, S. Ullah, K. Zhou, Q. Xia, H. Wang, S. Tu, J. Huang, H.-L. Xia, X.-Y. Liu, T. Thonhauser and J. Li, A Microporous Metal-Organic Framework Incorporating Both Primary and Secondary Building Units for Splitting Alkane Isomers, *J. Am. Chem. Soc.*, 2022, **144**, 3766–3770.
- 6 Y. Guo, K. Wang, Y. Hong, H. Wu and Q. Zhang, Recent progress on pristine two-dimensional metal-organic frameworks as active components in supercapacitors, *Dalton Trans.*, 2021, **50**, 11331–11346.
- 7 C. Li, Y. Yuan, M. Yue, Q. Hu, X. Ren, B. Pan, C. Zhang, K. Wang and Q. Zhang, Recent Advances in Pristine Iron Triad Metal-Organic Framework Cathodes for Alkali Metal-Ion Batteries, *Small*, 2023, 2310373.
- 8 J. D. Xiao and H. L. Jiang, Metal-Organic Frameworks for Photocatalysis and Photothermal Catalysis, *Acc. Chem. Res.*, 2019, **52**, 356–366.
- 9 J. Zhu, P.-Z. Li, W. Guo, Y. Zhao and R. Zou, Titanium-based metal-organic frameworks for photocatalytic applications, *Coord. Chem. Rev.*, 2018, **359**, 80–101.
- 10 L. Li, X.-S. Wang, T.-F. Liu and J. Ye, Titanium-Based MOF Materials: From Crystal Engineering to Photocatalysis, *Small Methods*, 2020, **4**, 2000486.
- 11 Y. Yan, C. Li, Y. Wu, J. Gao and Q. Zhang, From isolated Ti-oxo clusters to infinite Ti-oxo chains and sheets: Recent advances in photoactive Ti-based MOFs, *J. Mater. Chem. A*, 2020, **8**, 15245–15270.
- 12 C. Li, H. Xu, J. Gao, W. Du, L. Shangguan, X. Zhang, R.-B. Lin, H. Wu, W. Zhou, X. Liu, J. Yao and B. Chen, Tunable titanium metal-organic frameworks with infinite 1D Ti-O rods for efficient visible-light-driven photocatalytic H<sub>2</sub> evolution, *J. Mater. Chem. A*, 2019, **7**, 11928–11933.
- 13 P. Salcedo-Abraira, A. A. Babaryk, E. Montero-Lanzuela, O. R. Contreras-Almengor, M. Cabrero-Antonino, E. S. Grape, T. Willhammar, S. Navalon, E. Elkaim, H. Garcia and P. Horcajada, A Novel Porous Ti-Squarate as Efficient Photocatalyst in the Overall Water Splitting Reaction under Simulated Sunlight Irradiation, *Adv. Mater.*, 2021, **33**, 2106627.
- 14 B. Bueken, F. Vermoortele, D. E. Vanpoucke, H. Reinsch, C. C. Tsou, P. Valvekens, T. De Baerdemaeker, R. Ameloot, C. E. Kirschhock, V. Van Speybroeck, J. M. Mayer and D. De Vos, A Flexible Photoactive Titanium Metal-Organic Framework Based on a [Ti(IV)<sub>3</sub>(μ<sub>3</sub>-O)(O)<sub>2</sub>(COO)<sub>6</sub>] Cluster, *Angew. Chem., Int. Ed.*, 2015, **54**, 13912–13917.
- 15 S. Wang, M. Cabrero-Antonino, S. Navalón, C.-C. Cao, A. Tissot, L. Dovgaliuk, J. Marrot, C. Martineau-Corcós, L. Yu, H. Wang, W. Shepard, H. García and C. Serre, A Robust Titanium Isophthalate Metal-Organic Framework for Visible Light Photocatalytic CO<sub>2</sub> Methanation, *Chem*, 2020, **12**, 3409–3427.
- 16 A. Cadiou, N. Kolobov, S. Srinivasan, M. G. Goesten, H. Haspel, A. V. Bavykina, M. R. Tchalala, P. Maity, A. Goryachev, A. S. Poryvaev, M. Eddaoudi, M. V. Fedin, O. F. Mohammed and J. Gascon, A Titanium Metal-Organic Framework with Visible-Light-Responsive Photocatalytic Activity, *Angew. Chem., Int. Ed.*, 2020, **59**, 13468–13472.
- 17 Y. Sun, D.-F. Lu, Y. Sun, M.-Y. Gao, N. Zheng, C. Gu, F. Wang and J. Zhang, Large Titanium-Oxo Clusters as Precursors to Synthesize the Single Crystals of Ti-MOFs, *ACS Mater. Lett.*, 2021, **3**, 64–68.
- 18 H. Z. Li, Y. Pan, Q. H. Li, Q. P. Lin, D. Y. Lin, F. Wang, G. Xu and J. Zhang, Rationally designed titanium-based metal-organic frameworks for visible-light activated chemiresistive sensing, *J. Mater. Chem. A*, 2023, **11**, 965–971.

- 19 D.-F. Lu, Y.-P. Han, Y. Sun, F. Wang and J. Zhang, Titanium Sulfonate-Based Metal–Organic Frameworks, *Cryst. Growth Des.*, 2023, **23**, 3778–3784.
- 20 D.-F. Lu, S. Li, M.-X. Guan, Y.-P. Han, Y. Sun, X. Wu, F. Wang and J. Zhang, Visible-Light-Active Titanium Sulfonate Framework for Photocatalytic Organic Synthesis, *ACS Mater. Lett.*, 2023, **5**, 2836–2842.
- 21 J. Castells-Gil, N. Almora-Barrios, B. Lerma-Berlanga, N. M. Padial and C. Martí-Gastaldo, Chemical complexity for targeted function in heterometallic titanium–organic frameworks, *Chem. Sci.*, 2023, **14**, 6826–6840.
- 22 M. Dan-Hardi, C. Serre, T. Frot, L. Rozes, G. Maurin, C. Sanchez and G. Férey, A New Photoactive Crystalline Highly Porous Titanium(IV) Dicarboxylate, *J. Am. Chem. Soc.*, 2009, **131**, 10857–10859.
- 23 C. Zlotea, D. Phanon, M. Mazaj, D. Heurtaux, V. Guillerme, C. Serre, P. Horcajada, T. Devic, E. Magnier, F. Cuevas, G. Férey, P. L. Llewellyn and M. Latroche, Effect of NH<sub>2</sub> and CF<sub>3</sub> functionalization on the hydrogen sorption properties of MOFs, *Dalton Trans.*, 2011, **40**, 4879–4881.
- 24 Y. Fu, D. Sun, Y. Chen, R. Huang, Z. Ding, X. Fu and Z. Li, An amine-functionalized titanium metal-organic framework photocatalyst with visible-light-induced activity for CO<sub>2</sub> reduction, *Angew. Chem., Int. Ed.*, 2012, **51**, 3364–3367.
- 25 H. Assi, G. Mouchaham, N. Steunou, T. Devic and C. Serre, Titanium coordination compounds: from discrete metal complexes to metal-organic frameworks, *Chem. Soc. Rev.*, 2017, **46**, 3431–3452.
- 26 P. Coppens, Y. Chen and E. Trzop, Crystallography and properties of polyoxotitanate nanoclusters, *Chem. Rev.*, 2014, **114**, 9645–9661.
- 27 L. Zhang, X. Fan, X. Yi, X. Lin and J. Zhang, Coordination-Delayed-Hydrolysis Method for the Synthesis and Structural Modulation of Titanium-Oxo Clusters, *Acc. Chem. Res.*, 2022, **55**, 3150–3161.
- 28 H. L. Nguyen, F. Gandara, H. Furukawa, T. L. H. Doan, K. E. Cordova and O. M. Yaghi, A Titanium–Organic Framework as an Exemplar of Combining the Chemistry of Metal- and Covalent–Organic Frameworks, *J. Am. Chem. Soc.*, 2016, **138**, 4330–4333.
- 29 S. Wang, T. Kitao, N. Guillou, M. Wahiduzzaman, C. Martineau-Corcus, F. Nouar, A. Tissot, L. Binet, N. Ramsahye, S. Devautour-Vinot, S. Kitagawa, S. Seki, Y. Tsutsui, V. Briois, N. Steunou, G. Maurin, T. Uemura and C. Serre, A phase transformable ultrastable titanium-carboxylate framework for photoconduction, *Nat. Commun.*, 2018, **9**, 1660.
- 30 C. Li, H. Xu, J. Gao, W. Du, L. Shangguan, X. Zhang, R.-B. Lin, H. Wu, W. Zhou, X. Liu, J. Yao and B. Chen, Tunable titanium metal–organic frameworks with infinite 1D Ti–O rods for efficient visible-light-driven photocatalytic H<sub>2</sub> evolution, *J. Mater. Chem. A*, 2019, **7**, 11928–11933.
- 31 J. N. Chang, Q. Li, Y. Yan, J. W. Shi, J. Zhou, M. Lu, M. Zhang, H. M. Ding, Y. Chen, S. L. Li and Y. Q. Lan, Covalent-Bonding Oxidation Group and Titanium Cluster to Synthesize a Porous Crystalline Catalyst for Selective Photo-Oxidation Biomass Valorization, *Angew. Chem., Int. Ed.*, 2022, **61**, e202209289.
- 32 J. T. Bryant, M. W. Logan, Z. Chen, M. Djokic, D. R. Cairnie, D. A. Vazquez-Molina, A. Nijamudheen, K. R. Langlois, M. J. Markley, G. Pombar, A. A. Holland, J. D. Caranto, J. K. Harper, A. J. Morris, J. L. Mendoza-Cortes, T. Jurca, K. W. Chapman and F. J. Uribe-Romo, Synergistic Steric and Electronic Effects on the Photoredox Catalysis by a Multivariate Library of Titania Metal–Organic Frameworks, *J. Am. Chem. Soc.*, 2023, **145**, 4589–4600.
- 33 S. Smolders, T. Willhammar, A. Krajnc, K. Sentosun, M. T. Wharmby, K. A. Lomachenko, S. Bals, G. Mali, M. B. J. Roeyffers, D. E. De Vos and B. Bueken, A Titanium (IV)-based Metal–Organic Framework Featuring Defect-Rich Ti–O Sheets as an Oxidative Desulfurization Catalyst, *Angew. Chem., Int. Ed.*, 2019, **58**, 9160–9165.
- 34 S. Yuan, J. S. Qin, H. Q. Xu, J. Su, D. Rossi, Y. Chen, L. Zhang, C. Lollar, Q. Wang, H. L. Jiang, D. H. Son, H. Xu, Z. Huang, X. Zou and H. C. Zhou, [Ti<sub>8</sub>Zr<sub>2</sub>O<sub>12</sub>(COO)<sub>16</sub>] Cluster: An Ideal Inorganic Building Unit for Photoactive Metal–Organic Frameworks, *ACS Cent. Sci.*, 2018, **4**, 105–111.
- 35 Z. Huang, E. S. Grape, J. Li, A. K. Inge and X. Zou, 3D electron diffraction as an important technique for structure elucidation of metal-organic frameworks and covalent organic frameworks, *Coord. Chem. Rev.*, 2021, **427**, 213583.
- 36 J. Gao, J. Miao, P. Z. Li, W. Y. Teng, L. Yang, Y. Zhao, B. Liu and Q. Zhang, A p-type Ti(IV)-based metal-organic framework with visible-light photo-response, *Chem. Commun.*, 2014, **50**, 3786–3788.
- 37 H. Assi, L. C. P. Pérez, G. Mouchaham, F. Ragon, M. Nasalevich, N. Guillou, C. Martineau, H. Chevreau, F. Kapteijn, J. Gascon, P. Fertey, E. Elkaim, C. Serre and T. Devic, Investigating the Case of Titanium(IV) Carboxyphenolate Photoactive Coordination Polymers, *Inorg. Chem.*, 2016, **55**, 7192–7199.
- 38 N. M. Padial, J. Castells-Gil, N. Almora-Barrios, M. Romero-Angel, I. da Silva, M. Barawi, A. Garcia-Sanchez, V. A. D. L. P. O'Shea and C. Martí-Gastaldo, Hydroxamate Titanium–Organic Frameworks and the Effect of Siderophore-Type Linkers over Their Photocatalytic Activity, *J. Am. Chem. Soc.*, 2019, **141**, 13124–13133.
- 39 A. Schaate, P. Roy, A. Godt, J. Lippke, F. Waltz, M. Wiebecke and P. Behrens, Modulated synthesis of Zr-based metal-organic frameworks: from nano to single crystals, *Chem. – Eur. J.*, 2011, **17**, 6643–6651.
- 40 S. Yuan, T. F. Liu, D. Feng, J. Tian, K. Wang, J. Qin, Q. Zhang, Y. P. Chen, M. Bosch, L. Zou, S. J. Teat, S. J. Dalgarno and H. C. Zhou, A single crystalline porphyrinic titanium metal-organic framework, *Chem. Sci.*, 2015, **6**, 3926–3930.
- 41 G. Lan, K. Ni, S. S. Veroneau, X. Feng, G. T. Nash, T. Luo, Z. Xu and W. Lin, Titanium-Based Nanoscale Metal–Organic Framework for Type I Photodynamic Therapy, *J. Am. Chem. Soc.*, 2019, **141**, 4204–4208.



- 42 X. Feng, Y. Song, J. S. Chen, Z. Li, E. Y. Chen, M. Kaufmann, C. Wang and W. Lin, Cobalt-bridged secondary building units in a titanium metal-organic framework catalyze cascade reduction of N-heteroarenes, *Chem. Sci.*, 2019, **10**, 2193–2198.
- 43 Y. Keum, S. Park, Y. P. Chen and J. Park, Titanium-Carboxylate Metal-Organic Framework Based on an Unprecedented Ti-Oxo Chain Cluster, *Angew. Chem., Int. Ed.*, 2018, **57**, 14852–14856.
- 44 J. Castells-Gil, N. M. Padial, N. Almora-Barrios, I. da Silva, D. Mateo, J. Albero, H. García and C. Martí-Gastaldo, De novo synthesis of mesoporous photoactive titanium(iv)-organic frameworks with MIL-100 topology, *Chem. Sci.*, 2019, **10**, 4313–4321.
- 45 M. Y. Gao, Z. R. Wang, Q. H. Li, D. J. Li, Y. Y. Sun, Y. H. Andaloussi, C. Ma, C. H. Deng, J. Zhang and L. Zhang, Black Titanium-Oxo Clusters with Ultralow Band Gaps and Enhanced Nonlinear Optical Performance, *J. Am. Chem. Soc.*, 2022, **144**, 8153–8161.
- 46 O. V. Gutov, S. Molina, E. C. Escudero-Adan and A. Shafir, Modulation by Amino Acids: Toward Superior Control in the Synthesis of Zirconium Metal-Organic Frameworks, *Chem. – Eur. J.*, 2016, **22**, 13582–13587.
- 47 A. K. Bagdi, M. Rahman, D. Bhattacharjee, G. V. Zyryanov, S. Ghosh, O. N. Chupakhin and A. Hajra, Visible light promoted cross-dehydrogenative coupling: a decade update, *Green Chem.*, 2020, **22**, 6632–6681.