



Cite this: *CrystEngComm*, 2020, 22, 2889

Received 15th March 2020,
Accepted 6th April 2020

DOI: 10.1039/d0ce00397b

rsc.li/crystengcomm

Intrinsically porous molecular building blocks for metal organic frameworks tailored by the bridging effect of counter cations†

Peng Yang,^{ab} Buthainah Alshankiti^a and Niveen M. Khashab  [✉]

Predesigned organic linkers have dominated the world of pillared metal organic frameworks to tune the overall morphology, size, and performance of this class of materials. However, the porosity of the framework was never guaranteed due to possible assembly interpenetration and ligand self-closure. Here, we present an interesting construction strategy employing macrocyclic molecular building blocks (MBBs) with intrinsic voids to boost the porosity and host-guest interactions of these hybrid frameworks. *In situ* co-crystallization of the isolated polyoxomolybdates (P₂Mo₅O₂₃) and cyclodextrins (CDs) has resulted in seven POM-CD MOFs following this strategy. The bridging effect dictated by the size of counter cations (Na⁺, K⁺, and Cs⁺) can readily tune the structural and performance features of the end frameworks including pore morphology and water stability. This strategy paves the way for the precise design of customized porous materials with built-in macrocyclic hosts for improved molecular recognition of prospective guest molecules.

Inspired by the evolution of biological systems from simple units into a vast range of complex structures, scientists have directed their attention towards the rational design of self-organizing building blocks or supramolecular assembly of more intricate artificial systems. Developing superior smart materials has been pivotal to resolve industrial, environmental, and societal challenges.^{1–4} The concept of preparing “materials on demand” or tailoring material design has fueled this field for the last decade.⁵ Metal organic frameworks (MOFs) have proved to be a main player in this

field following the guidelines of reticular chemistry and the well-defined structures of their secondary building units (SBUs) or molecular building blocks (MBBs).⁶ Aside from the many attractive features of MOFs (*e.g.*, huge surface area and low crystal density), construction of networks with tailored porosity and a prospective application have been the main highlight.^{7–9}

A major drawback to the success of the rational and predesigned synthesis of robust porous materials has been the limited access to the pores within open structures.¹⁰ This is a critical aspect to the utility of these structures and occurs due to either self-interpenetration¹¹ as observed for very open frameworks or strong host-guest interactions that lead to the destruction of the host framework when removal or exchange of guests is attempted.¹² As a result, the development of reliable and reproducible methods to achieve robust porous frameworks with tailored structures and tunable properties remains a considerable challenge.

The classical “pillar” construction principle, which mainly relies on synthesizing and tailoring the organic ligand, is the most used strategy for the precise modification of the pores and the topologies of MOFs (Fig. 1). Naturally occurring γ -cyclodextrin (γ -CD) have been successfully used in building CD-MOFs with permanent porosity and the ability to store small molecules in their pores.^{13–15} Recently, we have communicated the use of CDs combined with inorganic polyoxometalates (POMs)^{16–18} as MBBs to prepare a new generation of porous hybrid frameworks (POM-CD MOFs).¹⁹ These assemblies benefited from the intrinsic microporosity and functional multiplicity of both isolated building blocks. This promoted a different strategy in the construction of porous frameworks by employing macrocyclic MBBs (Fig. 1). A library of customized porous structures could now be prepared on-demand by choosing the right macrocyclic MBBs. More importantly, we prove that mechanistically the counter cations do not only balance the charge, but play a critical role as “a bridge” to connect these building blocks. We investigated the bridging effect of different counter cations of

^a Smart Hybrid Materials Research Group (SHMs), Advanced Membranes and Porous Materials Center (AMPMC), King Abdullah University of Science and Technology (KAUST), Thuwal 23955, Saudi Arabia.

E-mail: niveen.khashab@kaust.edu.sa

^b College of Chemistry and Chemical Engineering, Hunan University, Changsha 410082, P.R. China

† Electronic supplementary information (ESI) available. CCDC 1963899, 1963900 and 1963902–1963906. For ESI and crystallographic data in CIF or other electronic format see DOI:10.1039/d0ce00397b



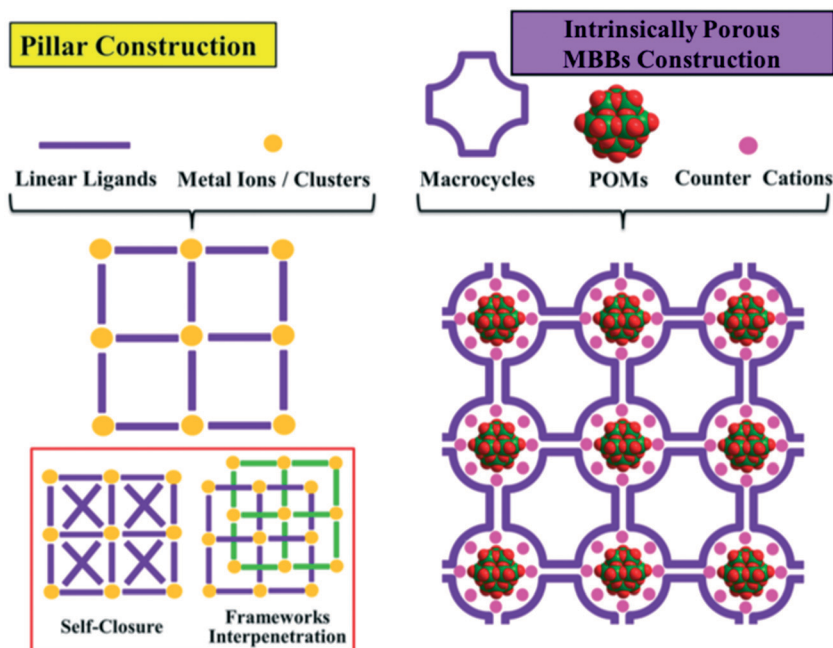


Fig. 1 Illustration of the pillar and intrinsically porous MBBs construction strategies in MOF chemistry.

alkali metals (Na^+ , K^+ , and Cs^+), of which the size had a direct effect on the structural features of the corresponding POM-CD MOFs, for example, porosity factors and pore shape.

Results and discussion

All seven compounds were synthesized by the reaction of CDs with 85% H_3PO_4 and $\text{Na}_2\text{MoO}_4 \cdot 2\text{H}_2\text{O}$ in acetate buffers involving different alkali metal ions (*e.g.*, Na^+ , K^+ , and Cs^+), and isolated as protonated single/mixed cation salts $\text{H}_2\text{Na}_{22}[\text{P}_2\text{Mo}_5\text{O}_{23}]_4[\alpha\text{-CD}]_4 \cdot 7\text{CH}_3\text{COOH} \cdot 48\text{H}_2\text{O}$ (**Na-PMo- α -CD**), $\text{H}_{2.5}\text{K}_{11.5}\text{Na}_{10}[\text{P}_2\text{Mo}_5\text{O}_{23}]_4[\alpha\text{-CD}]_4 \cdot \text{CH}_3\text{COOH} \cdot 35\text{H}_2\text{O}$ (**K-PMo- α -CD**), $\text{H}_{1.5}\text{Cs}_{4.5}\text{Na}_6[\text{P}_2\text{Mo}_5\text{O}_{23}]_2[\alpha\text{-CD}]_2 \cdot 3\text{CH}_3\text{COOH} \cdot 30\text{H}_2\text{O}$ (**Cs-PMo- α -CD**), $\text{H}_5\text{Na}_{19}[\text{P}_2\text{Mo}_5\text{O}_{23}]_4[\beta\text{-CD}]_4 \cdot 2\text{CH}_3\text{COONa} \cdot 42\text{H}_2\text{O}$

(**Na-PMo- β -CD**), $\text{H}_3\text{Na}_{21}[\text{P}_2\text{Mo}_5\text{O}_{23}]_4[\gamma\text{-CD}]_2 \cdot 7\text{CH}_3\text{COONa} \cdot 56\text{H}_2\text{O}$ (**Na-PMo- γ -CD**), $\text{H}_4\text{K}_{20}\text{Na}_2[\text{P}_2\text{Mo}_5\text{O}_{23}]_4[\gamma\text{-CD}]_2 \cdot 2(\text{CH}_3\text{COO}) \cdot 48\text{H}_2\text{O}$ (**K-PMo- γ -CD**), and $\text{H}_{3.5}\text{Cs}_{5.5}\text{Na}_6[\text{P}_2\text{Mo}_5\text{O}_{23}]_2[\gamma\text{-CD}] \cdot 3(\text{CH}_3\text{COO}) \cdot 37\text{H}_2\text{O}$ (**Cs-PMo- γ -CD**), respectively.

Self-assembly of the *in situ* formed $\{\text{P}_2\text{Mo}_5\text{O}_{23}\}$ (P_2Mo_5) with $\alpha\text{-CD}$ in $\text{NaCH}_3\text{COO}/\text{CH}_3\text{COOH}$ buffer (pH 4) has resulted in a three-dimensional (3D) framework of **Na-PMo- α -CD** as seen by X-ray structural analysis (Fig. 2). The asymmetric unit is composed of four crystallographically independent $\alpha\text{-CD}$ s and P_2Mo_5 ligated mainly by Na^+ cations, of which the coordination spheres are fulfilled by oxygen atoms from the hydroxy groups of $\alpha\text{-CD}$ s and terminal oxygens of P_2Mo_5 in concert with water molecules. As viewed from *a* axis, the skeleton of **Na-PMo- α -CD** is built upon



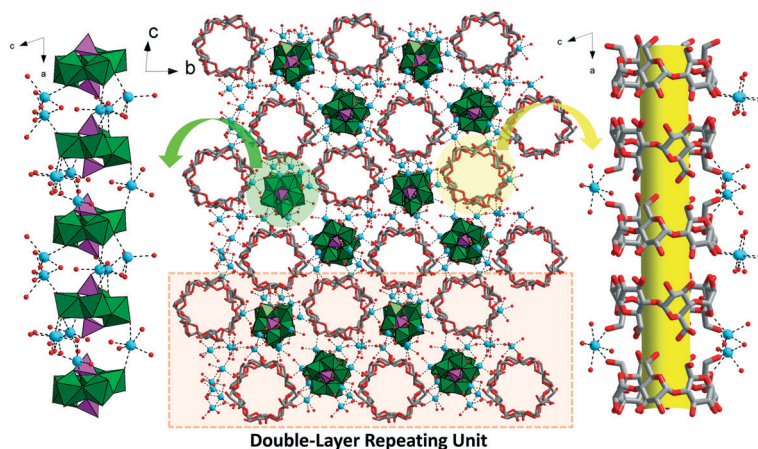


Fig. 2 Combined polyhedral/ball-and-stick representation of **Na-PMo- α -CD**. Color code: MoO_6 , green octahedra; PO_4 pink tetrahedra; Na, turquoise; O, red; C, gray.



Intrigued by the bridging effect of the counter cations, we set about exploring the structural influence provided by homologous CDs. Single-crystal XRD reveals that, albeit the same Na⁺ cation media, the size of CD macrocycles could heavily impact the detailed structural arrangement of the inorganic/organic MBBs in **Na-PMo-β-CD** and **Na-PMo-γ-CD** as

Apart from the aforementioned structural tunability, it is worth to stress the distinct characters of each CD analogue in the synthetic strategies of the PMo-CD MOFs. The family of **Na/K/Cs-PMo- α -CD**, for example, could be obtained at pH 4 rather than pH 5. It is presumed that the $\text{pH} < \text{p}K_{\text{a}}$ (HOAc,



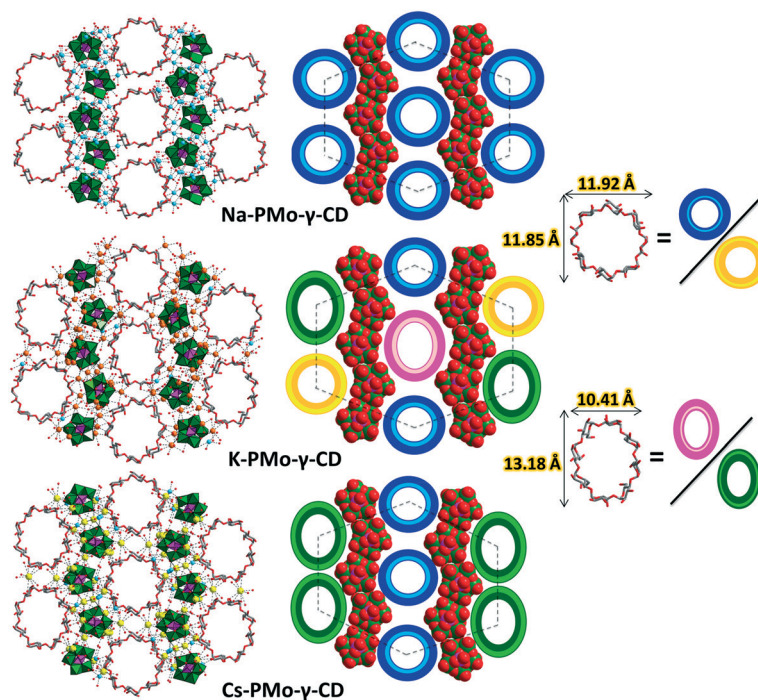


Fig. 5 Pore-shape distortion affected by the bridging effect of counter cations in Na/K/Cs-PMo- γ -CD. Different aspect ratios and orientations of γ -CDs have been highlighted by various colors (distorted pink and green).

pK_a 4.76) could strengthen the multiple hydrogen bonding interactions between the accommodated HOAc guest molecules and the hydroxy groups of α -CD hosts, thereby stabilizing the whole frameworks. Being verified by FT-IR spectra (Fig. S3–S5[†]), the adsorption peak centered at 1710 cm^{-1} declares the presence of HOAc molecules rather than acetate salts in the solid states of Na/K/Cs-PMo- α -CD. As to Na-PMo- β -CD, it could be prepared under both pH 4 and 5, but in Na⁺-containing media only. The appearance of K⁺ or Cs⁺ would precipitate the β -CD rapidly which could be assigned to its low water solubility (18.5 g L^{-1} , $25\text{ }^\circ\text{C}$). Finally for Na/K/Cs-PMo- γ -CD, the same structures could be obtained under single/mixed cation environments at both pH 4 and 5, which might be ascribed to the uniform layered pattern of P_2Mo_5 , featuring better environmental compatibility in the crystal lattices than the embedded coupled dimer of Na/K/Cs-PMo- α -CD and Na-PMo- β -CD. Moreover, in spite of the good stability of these PMo-CD MOFs in most common organic solvents (*e.g.*, methanol, acetone, and acetonitrile), the Na/K-PMo-CD MOFs could easily decompose in water as confirmed by NMR studies (Fig. S6–S11[†]). However, the large cations of Cs⁺ could remarkably enhance the stability of the framework of Cs-PMo- γ -CD in aqueous media (Fig. S12[†]), which could be explained by the “normal solubility trend” in POM chemistry.²⁰

Conclusions

Without the tedious synthesis of new organic ligands required for the classical pillared MOF synthesis, the

intrinsically porous MBBs construction strategy paves the way for a facile approach not only for the rational design of molecular-level controlled porous materials, but also for their property optimization and function expansion. Our research results show that the size of counter cations could easily program the structural features of POM-CD MOFs as well as their water stability. Using Cs⁺ cations, the framework showed an enhanced water stability in addition to selective guest molecules separation by the distortional CD macrocycles. This strategy can be furthermore expanded to include other macrocycles such as cucurbiturils and pillararenes, of which the frameworks have been already acquired and will be the subject of future reports.

Methods

Experimental results (crystallographic data, elemental analysis, FT-IR spectra, TGA diagrams, powder XRD patterns, multinuclear (^1H , ^{13}C , and ^{31}P) NMR spectra) can be found in the Supplementary Information.

Synthesis of $\text{H}_2\text{Na}_{22}[\text{P}_2\text{Mo}_5\text{O}_{23}]_4[\alpha\text{-CD}]_4 \cdot 7\text{CH}_3\text{COOH} \cdot 48\text{H}_2\text{O}$ (Na-PMo- α -CD)

To a solution of α -cyclodextrin (0.097 g, 0.100 mmol) in 5 mL 1 M $\text{NaCH}_3\text{COO}/\text{CH}_3\text{COOH}$ buffer (pH 4.0), 85% H_3PO_4 (50 μL), and $\text{Na}_2\text{MoO}_4 \cdot 2\text{H}_2\text{O}$ (0.242 g, 1.000 mmol) were added successively upon stirring. The solution was then stirred for 1 hour at $80\text{ }^\circ\text{C}$. The clear colorless solution was cooled to room temperature, filtered, and the filtrate was allowed to evaporate in an open vial at room temperature. The block-



CrystEngComm, 2020, 22, 2889–2894 | 2893

- 8 Z. R. Herm, *et al.*, Separation of hexane isomers in a metal-organic framework with triangular channels, *Science*, 2013, **340**, 960–964.
- 9 J.-M. Lin, *et al.*, A metal-organic framework with a pore size/shape suitable for strong binding and close packing of methane, *Angew. Chem., Int. Ed.*, 2016, **55**, 4674–4678.
- 10 M. Eddaoudi, *et al.*, Modular chemistry: secondary building units as a basis for the design of highly porous and robust metal-organic carboxylate frameworks, *Acc. Chem. Res.*, 2001, **34**, 319–330.
- 11 S. R. Batten and R. Robson, Interpenetrating nets: ordered, periodic entanglement, *Angew. Chem., Int. Ed.*, 1998, **37**, 1460–1494.
- 12 O. M. Yaghi, H. Li, C. Davis, D. Richardson and T. L. Groy, Synthetic strategies, structure patterns, and emerging properties in the chemistry of modular porous solids, *Acc. Chem. Res.*, 1998, **31**, 474–484.
- 13 R. A. Smaldone, *et al.*, Metal–Organic Frameworks from Edible Natural Products, *Angew. Chem., Int. Ed.*, 2010, **49**, 8630–8634.
- 14 R. S. Forgan, *et al.*, Nanoporous Carbohydrate Metal–Organic Frameworks, *J. Am. Chem. Soc.*, 2012, **134**, 406–417.
- 15 H. A. Patel, *et al.*, Noninvasive Substitution of K⁺ Sites in Cyclodextrin Metal–Organic Frameworks by Li⁺ Ions, *J. Am. Chem. Soc.*, 2017, **139**, 11020–11023.
- 16 D. L. Long, R. Tsunashima and L. Cronin, Polyoxometalates: Building Blocks for Functional Nanoscale Systems, *Angew. Chem., Int. Ed.*, 2010, **49**, 1736–1758.
- 17 H. N. Miras, J. Yan, D. L. Long and L. Cronin, Engineering Polyoxometalates with Emergent Properties, *Chem. Soc. Rev.*, 2012, **41**, 7403–7430.
- 18 U. Kortz, *et al.*, Polyoxometalates: Fascinating Structures, Unique Magnetic Properties, *Coord. Chem. Rev.*, 2009, **253**, 2315–2327.
- 19 P. Yang, *et al.*, Polyoxometalate–cyclodextrin metal–organic frameworks: from tunable structure to customized storage functionality, *J. Am. Chem. Soc.*, 2019, **141**, 1847–1851.
- 20 A. Misra, K. Kozma, C. Streb and M. Nyman, Beyond charge balance: counter-cations in polyoxometalate chemistry, *Angew. Chem., Int. Ed.*, 2019, **58**, 2–19.

