

PAPER

[View Article Online](#)
[View Journal](#) | [View Issue](#)Cite this: *Dalton Trans.*, 2025, **54**, 8800

Rationally tailored passivator with multisite surface-anchors for suppressing ion migration toward air-stable perovskite solar cells†

Dandan Luo,^b Dingyu Xia,^b Fei Wang,^{*a} Chong Jia,^b Qiang Zhao,^{c,d} Xinhua Li^{c,d}  and Yiqing Chen^b  ^{*b}

Trap states in perovskite films fabricated using the solution method can capture photo-generated carriers, expedite ion migration, and contribute to decomposition of the perovskite layer, thereby emerging as a major threat to the commercialization of perovskite solar cells (PSCs). To address these issues, passivation of the surface traps on perovskite films *via* molecules with functional groups is proven to be one of the most effective tactics for obtaining high-performance PSCs. Herein, potassium nonafluoro-1-butanefluorophosphate (KNFBS) molecules with multiple chemical bonds, including multisite F atoms, sulfonic acid groups and K ions, were introduced as surface-anchoring passivators to improve the film quality and passivate trap states. Based on *in situ* conductive atomic force microscopy (C-AFM) and Kelvin probe force microscopy (KPFM) results, it was found that undercoordinated Pb and I vacancy defects on the surface and grain boundaries (GBs) of perovskite films can be synergistically curtailed *via* multiple chemical interactions, including Lewis acid–base, hydrogen and ionic bonds. Moreover, the influence of varied ligands on defects and halide ion migration in perovskites as well as the mechanism behind it were extensively explored. Therefore, the KNFBS-treated perovskite films with a more homogeneous surface potential distribution significantly reduced point and vacancy defects and dangling bond density, facilitated charge transfer, exhibited an optimized power conversion efficiency (PCE) of 20.88% and enhanced air stability for the PSCs fabricated and stored in fully open-air conditions. The work has not only elucidated the fundamental mechanisms of ion migration and multisite passivation at the surface and GBs of perovskites but also probes into ligand design strategies for further improving the performance of perovskite photovoltaics.

Received 14th February 2025,
Accepted 23rd April 2025

DOI: 10.1039/d5dt00352k

rsc.li/dalton

1. Introduction

Metal halide perovskite materials have developed into a game-changer in the optoelectronics field owing to their exceptional optoelectronic properties including regulable bandgaps, convenient solution preparation, and high defect tolerance.^{1–3} A certified power conversion efficiency (PCE) ranging from 3.8% to over 26.1% has been reported for perovskite solar cells (PSCs) in the last decade or so.^{4,5} However, the impending

problem of poor stability has been a bottleneck to further promote the commercial development of PSCs in the photovoltaic field.⁶ The instability of perovskite materials generally results from their ionic crystal nature and the traps produced during solution-based film preparation. First, the trap states in the bulk and interface of perovskite films, especially between the crystal grains, usually act as carrier recombination centers and subsequently result in defect-induced performance reduction.^{7,8} Second, research suggests that the performance deterioration of devices can be accelerated because the trap states are the center of instability and can easily induce the degradation of perovskites by the volatile environment, such as light, heat radiation and moisture.^{9,10} Third, grain boundaries (GBs) rich in a number of traps can serve as ion transport channels and generate serious outcomes, such as aggravation of current hysteresis in *J–V* characteristics and even reactions with the silver electrodes of PSCs.^{11,12}

In view of the previously mentioned problems caused by trap states existing in GBs and the surface of perovskite films,

^aSchool of Physics, Hefei University of Technology, Hefei, Anhui, 230009, People's Republic of China. E-mail: wangfei1213@hfut.edu.cn^bSchool of Materials Science and Engineering, Hefei University of Technology, Hefei, Anhui, 230009, People's Republic of China. E-mail: chenyaq63@126.com^cSchool of Mathematics and Physics, Anhui Jianzhu University, Hefei, 230601, China^dAnhui Research Center of Generic Technology in New Display Industry, Hefei, 230601, China†Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d5dt00352k>

a series of strategies has been undertaken to improve the properties of GBs, including composition, additive, solvent and processing engineering.^{13–15} Among them, GB additives have been developed to mitigate the trap state *via* chemically varied anchors including hydrogen bonds, conjugated bonds, *etc.*^{16–18} GB passivators usually include electron donor/acceptor molecules, metal ions, Pb-based complexes, quantum dots, ionic liquid, *etc.*^{19–24} For example, Lewis-based molecules containing S, N, and O atoms display excellent effects of trap mitigation *via* reduction of the shallow trap state at GBs because their electron-donating ability can share with the empty 6p orbital on Pb²⁺ ions of the perovskite.^{25,26} Alkali metal ions with low site resistances can permeate into the perovskite lattice and exert the dielectric screening effect, resulting in the promotion of grain growth, elimination of I[−] chelate and subsequent passivation of Frenkel traps at GBs.^{27,28} Organic optoelectronic molecules such as (phenylsulfonyl)pyrrole (PSP), DMAcPA, *etc.* chemically anchored on the surface and GBs have been proved to reduce interfacial voids and compositional heterogeneity in the perovskite surface *via* the formation of a “molecular lock”.^{29,30}

However, there have been varied challenges for the up-to-date trap passivator in GBs. First, it is tough to carry out the *in situ* characterization to verify the GB agents due to the difficulties of their penetration in the entire GBs. Secondly, the GB passivator can hardly play multifunctional roles to deactivate the trap state resulting from the lack of synergistic design. Thirdly, the elaborate control of non-excess penetration into the perovskite lattice is needed to release GB strain and strengthen the GB structure. Inspired by the above challenges, potassium nonafluoro-1-butananesulfonate (KNFBS) was targeted as a novel anionic surfactant with multi-action sites for use as a GB and surface passivator. The KNFBS additive with three different kinds of chemical anchors, including multi-F atoms, alkali metal K⁺, and sulfonic acid group S=O can play cooperative roles in GB passivation. Although the passivation effect based on the single functional group is well-known, the synergistic effect included in one GB passivator has rarely been explored. Moreover, it is not clear whether the GB additives have penetrated into GBs and stayed inside. Therefore, a thorough exploration was conducted to provide direct evidence of GBs permeation and subsequently obtain a comprehensive understanding of an underlying mechanism of GB passivation using Kelvin probe microscopy (KPFM) and conductive atomic force microscopy (c-AFM). Profiting from the trap passivation due to the multi-functional groups of KNFBS additives, the champion PCE of KNFBS-treated devices is raised to 20.88% with a high V_{oc} of 1.10 V, J_{sc} of 24.18 mA cm^{−2}, and FF of 78.81%. In addition, the unencapsulated KNFBS-treated cells can maintain 82% of its initial efficiency in an ambient environment with a relative humidity of 35 ± 5%, while the pristine device declined to 58% after more than 42 d. This study put forward a novel agent for the surface and GB passivation and elucidated the underlying mechanism of suppression of ion migration, which is expected to offer more rational tailoring of multifunctional agents.

2. Results and discussion

Steady-state (PL) measurements are conducted to evaluate the recombination characteristic of perovskite film based on the distinct configuration of FTO/perovskite and FTO/perovskite/HTM, as plotted in Fig. 1a and b, respectively. It is observed that the PL peaks at 768 nm correspond to all the as-prepared perovskite samples. Beyond that, the intensity of thin film containing 1.5 mg mL^{−1} KNFBS was approximately five times higher than the reference, indicating more abundant production of light-induced electrons due to the improvement of crystallization and light absorption after KNFBS treatment. The PL intensity of the target films were significantly diminished compared with the control (Fig. 1b), indicating that alleviation of carrier recombination can facilitate electron extraction at the perovskite/HTM interface.³¹

X-ray diffraction (XRD) measurements were exerted to explore the effect of KNFBS agents on the crystallinity properties of perovskite film. The XRD results of the perovskite samples are presented in Fig. S1a,† with the peak at 14.0° corresponding to the (100) plane of the perovskites.³² The negligible alteration of the diffraction peak position of the as-prepared samples after KNFBS passivation indicates their similarity in crystal structure. Fig. S1b† presents the full-width-at-half-maximum (FWHM) and peak intensity of the perovskites at 14.0°. Thus, the KNFBS-treated perovskite layer manifests a narrower half-width and higher peak intensity, indicating better crystallization of the as-prepared films with diminished defects.

The UV-visible absorption spectra are conducted to investigate the influence of KNFBS on the perovskites. As shown in Fig. S1c,† the absorbance intensity of KNFBS-added film is higher both in the visible and the infrared region compared with the control sample, which is attributable to the better film quality and enlarged crystal grains (as depicted in Fig. 3a and b). Photon capture and the subsequent current density of the devices can be improved for the higher absorbance intensity of passivated perovskite film. Notably, an undistorted crystal structure of perovskites was confirmed by the insignificant changes in the optical bandgap (E_g) of 1.576 eV calculated by the Tauc plots in the inset.

To estimate the trap density of the as-prepared films, space charge limited current (SCLC) measurements were exerted on hole-only devices in Fig. 1c and d, which were depicted in the logarithmic scale. Three distinct regions were observed at low, intermediate and higher biases, standing for the ohmic, the trap-filled limited and trap-free SCLC region, respectively. Generally, the point of intersection between intermediate and higher biases regions determines the value of trap-filled limit voltage (V_{TFL}).^{33,34} Subsequently, the trap densities N_{trap} can be supposed by the following equation:³⁵

$$N_{trap} = \frac{2\epsilon_0\epsilon_r V_{TFL}}{eL^2} \quad (1)$$

where e , ϵ_0 , ϵ_r and L represent the elementary charge, the vacuum permittivity, the relative dielectric constant of perovs-

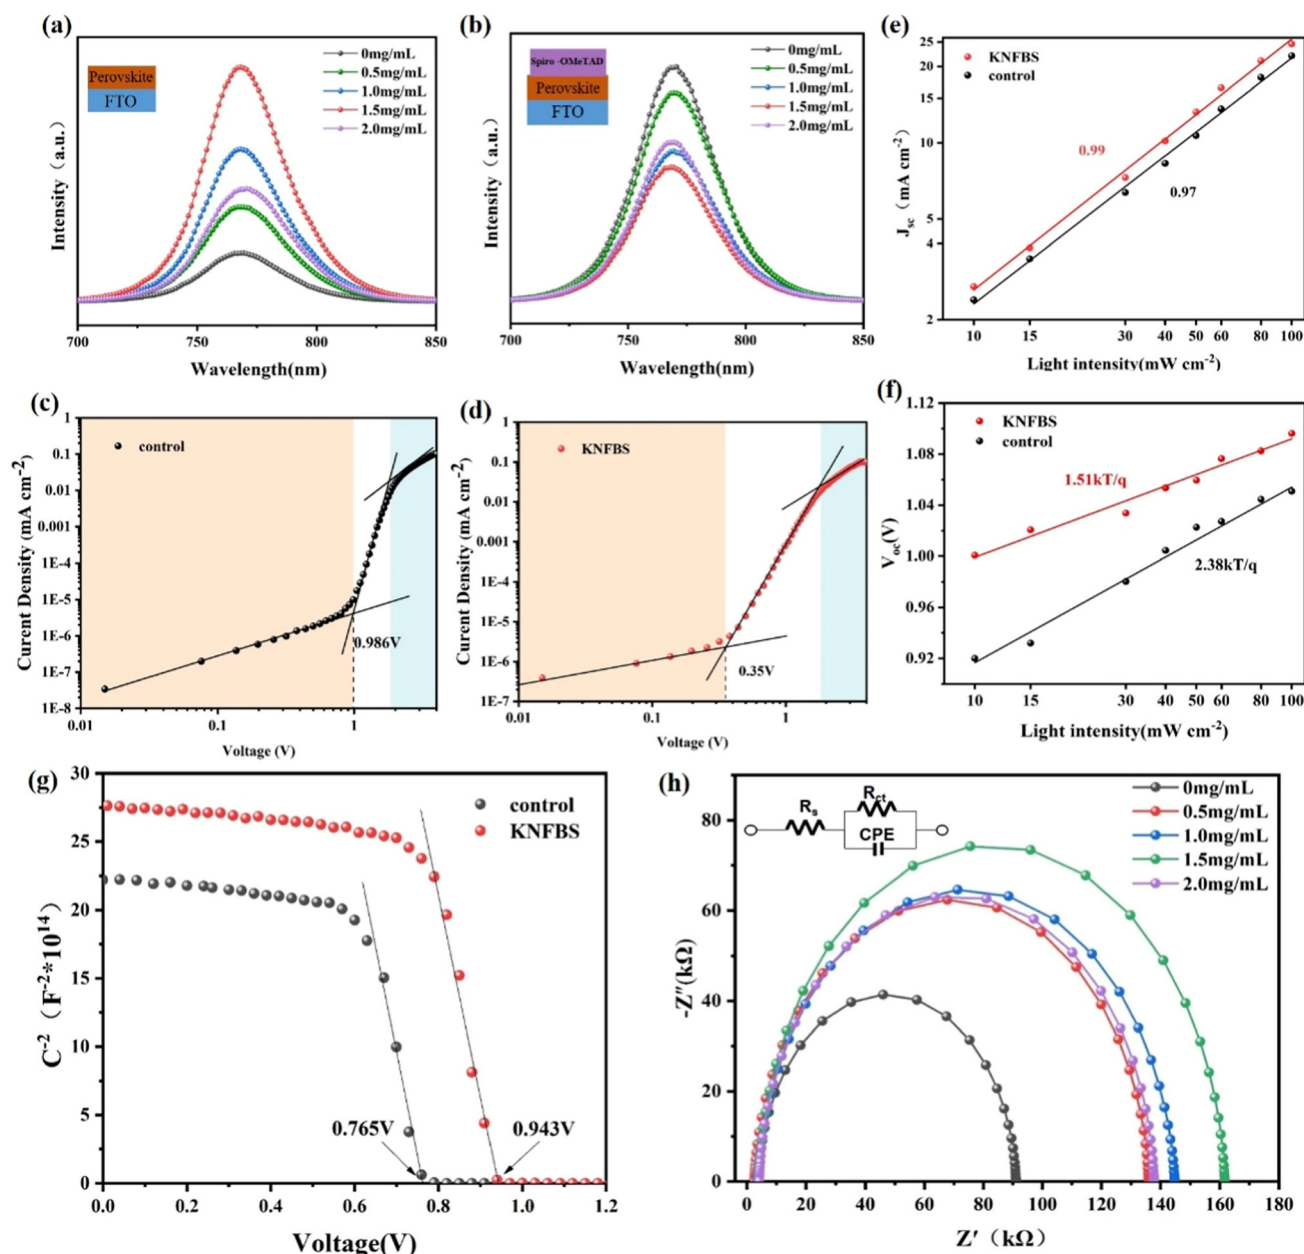


Fig. 1 Steady-state PL spectra based on the active layer (a) without and (b) with the HTL layer. Space-charge-limited current (SCLC) curves of the hole-only devices: (c) control and (d) with 1.5 mg mL⁻¹ KNFBS agents. Light intensity-dependent: (e) V_{oc} and (f) J_{sc} . (g) Mott-Schottky plots. (h) Nyquist plots of EIS in the dark with the corresponding equivalent circuits for fitting in the inset.

kite film ($\epsilon_r = 32$) and the film thickness, respectively. The reduction of the V_{TFL} value was observed for cells after KNFBS passivation, leading to the decrease of N_{trap} from 2.35×10^{16} to 7.24×10^{15} cm⁻³. The result indicates that mitigation of the carrier trap states through the diminished GB density can lead to the enhanced V_{oc} and FF.³⁶

Apart from N_{trap} , the Mott-Gurney law could be exerted to evaluate the carrier mobility (μ) by fitting the J - V curves:

$$J = \frac{9}{8} \epsilon_r \epsilon_0 \mu \frac{V^2}{L^3} \quad (2)$$

where J refers to the dark current density. As shown in Fig. S2a,† the hole mobilities were promoted from 1.83×10^{-5} to 4.61×10^{-5} cm² V⁻¹ s⁻¹, which indicates that the KNFBS-assisted film has eliminated the trap state of the target film compared with that of the control.³⁷ Faster hole transport can alleviate carrier accumulation at the HTL/perovskite interface.

The relationship between light intensity and J_{sc} as well as light intensity and V_{oc} was investigated to probe the effect of KNFBS agents on carrier transport and recombination properties. Generally speaking, there are two types of carrier recombination processes. One is single-molecular recombina-

tion, referring to the recombination of only one carrier (electron or hole), and the other is biomolecular recombination, referring to the recombination of both electrons and holes during the process. The following power-law behavior was confirmed by the J_{sc} and light intensity:³⁸

$$J_{sc} = I^\alpha \quad (3)$$

where I and α signify the light intensity and the exponent of the power law. If α is closer to 1, biomolecular recombination is lower. As depicted in Fig. 1e, the fitting α value for the pristine and target devices was 0.97 and 0.99, respectively, implying minimized recombination of excitons. The ideality factor η values of V_{oc} under changing light intensity can be described as the following relationship:³⁸

$$V_{oc} = V_s + \frac{\eta k_B T}{q} \ln I \quad (4)$$

in which V_s represents the open-circuit voltage under standard solar illumination (AM 1.5), I represents the light intensity, q is the electron charge, k_B is the Boltzmann constant and T is the temperature. Fig. 1f depicted a linear relationship between V_{oc} and the logarithm of light intensity with a slope of $\eta k_B T/q$. The KNFBS-processed device holds a smaller slope of $1.51 k_B T/q$ than the pristine device with a slope of $2.38 k_B T/q$. Generally, a larger η than 1 implies predominant single-molecular recombination and a value of η closer to 1 indicates suppressed defect-assist recombination.³⁹ The results demonstrate the diminished defect-induced carrier recombination and the intrinsic trap density, resulting from the enhanced crystal quality and anchored ions after the KNFBS treatment.

The built-in voltage (V_{bi}) of cells can be obtained *via* the Mott-Schottky plots, in which V_{bi} is calculated according to the following equation:⁴⁰

$$C = \left[\frac{-2e(V - V_{bi})}{qN} \right]^{-\frac{1}{2}} \quad (5)$$

where V , N , q , and C correspond to the bias voltage, minority doping concentration, electron charge and capacitance, respectively. V_{bi} signifies the depletion region length and can be determined from the C^{-2} - V plot. As shown in Fig. 1g, the higher V_{bi} value of the KNFBS-processed device (0.943 V) compared with the pristine device (0.765 V) can be ascribed to the diminished charge accumulation at the perovskite interface. The higher V_{bi} manifests a larger driving force for carrier separation, reduction of recombination, and ultimately increases V_{oc} .⁴¹ Electrical impedance spectroscopy (EIS) measurements were conducted to probe carrier recombination and defect-related characteristic of the PSCs. Fig. 1h depicted Nyquist plots under dark conditions containing the equivalent circuit model in the inset and the corresponding fitting parameters summarized in Table 1, in which R_s represents series resistance, R_{ct} represents recombination resistance, and CPE represents capacitance. R_s can be governed by the intercept point of the semicircle located at the high-frequency (HF) regions.⁴² The R_{ct} value for the KNFBS-treated device was significantly raised to $1.6 \times 10^5 \Omega$,

Table 1 EIS fitting parameters of control and KNFBS agent-based devices

KNFBS concentration (mg mL ⁻¹)	R_s (Ω)	R_{ct} (Ω)	CPE-T	CPE-P	τ_n (ms)
0	32.33	91 059	2.38×10^{-8}	0.97	1.75
0.5	29.49	137 891	2.54×10^{-8}	0.95	2.60
1.0	30.59	144 742	2.16×10^{-8}	0.94	2.22
1.5	24.41	161 620	2.12×10^{-8}	0.96	2.77
2.0	38.03	136 035	2.31×10^{-8}	0.96	2.42

whereas the pristine cell demonstrated a value of $9.1 \times 10^4 \Omega$. Generally, the carrier recombination lifetime (τ_n) is one of the crucial factors that can significantly exert influence on the PCE of solar cells, and it can be calculated from the equation $\tau_n = R_{ct} \times CPE$.⁴³ The value of τ_n for the target cell was 2.77 ms, in contrast to the value of 1.75 ms for the reference. Thus, the impressively larger R_{ct} and τ_n of the KNFBS-treated cell can result in raised V_{oc} and FF, due to optimized carrier transport and inhibited non-radiative carrier recombination.⁴⁴

Furthermore, EIS was carried out under different bias voltages to explore the rate of ion migration after the introduction of KNFBS agents. Fig. S3a to Fig. S3b† displays Nyquist plots under different bias containing the equivalent circuit model in the inset and the corresponding fitting parameters are summarized in Tables S1 and S2.† Similar to the R_s , R_{ct} and CPE in the equivalent circuit of the middle frequency (MF) region of Fig. 1h, a new fitting element, W_s , represents diffusion impedance at low frequency (LF) region. Recent studies have demonstrated that the signal in HF (high frequency) is consistent with fast electronic processes, while that in LF is consistent with electrochemical processes such as ion diffusion and electrochemical reactions.⁴⁵ The effect of KNFBS agents on τ_n was similar to the results displayed in Table 1. Interestingly, when bias voltage increased, a single recombination semicircle was observed in the MF region, indicating that only one type of carrier (electronic) transport is predominant under dark conditions, which is attributed to carrier trapping and surface recombination.⁴⁶ Based on the calculation of ion diffusion coefficient (D_{ion}), the slope of the Z'' curve in the image of Z'' as a function of $\omega^{-1/2}$ in Fig. S3e,† extracted from the spectrum of the LF region in Fig. S3d,† can be used to evaluate the value of the Warburg coefficient: σ_w . The value of the corresponding slope in Fig. S3e† is directly proportional to the value of σ_w and $D_{ion} \propto \frac{1}{\sigma_w^2}$.⁴⁷ The KNFBS-based device presents a larger value of σ_w and a reduced value of D_{ion} , indicating suppressed ion migration after the introduction of KNFBS agents.

To understand the impact of the concentration of KNFBS on photovoltaic performance, J - V curves of the champion devices based on 0.5, 1, 1.5, and 2 mg mL⁻¹ of KNFBS agents were compared in Fig. 2a and the corresponding photovoltaic characteristics are displayed in Table 2. Compared with the reference device, 1.5 mg mL⁻¹ of KNFBS remarkably raises all the photovoltaic parameters of PSCs: V_{oc} , J_{sc} , and the fill factor (FF). The best PCE of the reference device was 17.24%, with an

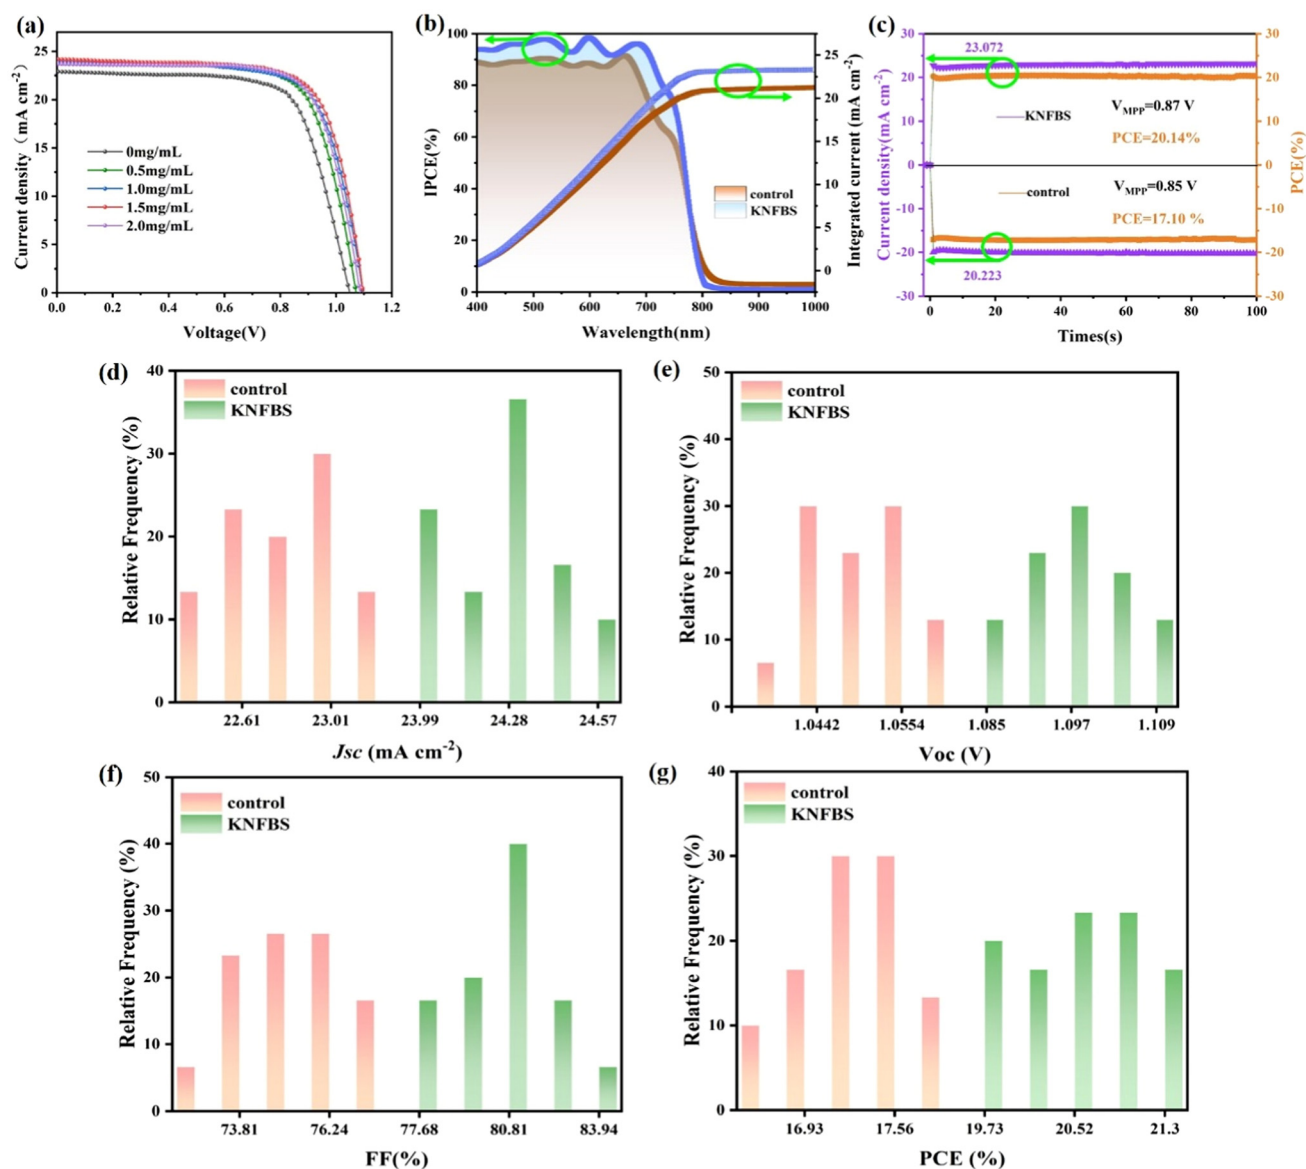


Fig. 2 Photovoltaic performance of pristine and KNFBS-treated devices: (a) $J-V$ curves; (b) IPCE curves. (c) Stabilized PCE and J_{sc} at the maximum power point (MPP) output. Statistical photovoltaic parameter distribution obtained from 30 devices: (d) J_{sc} ; (e) V_{oc} ; (f) FF; (g) PCE.

Table 2 Device performances based on pristine and KNFBS additive-containing perovskite films

KNFBS (mg mL^{-1})		V_{oc} (V)	J_{sc} (mA cm^{-2})	FF (%)	PCE (%)
0	Best	1.048	22.88	71.84	17.24
	Average	1.048 ± 0.015	22.71 ± 0.5	71.65 ± 2.74	17.16 ± 0.87
0.5	Best	1.071	23.96	75.01	19.24
	Average	1.071 ± 0.012	23.83 ± 0.86	74.68 ± 3.3	18.57 ± 1.68
1.0	Best	1.095	23.88	77.23	20.19
	Average	1.091 ± 0.019	23.54 ± 0.52	76.02 ± 4.17	19.53 ± 1.3
1.5	Best	1.096	24.18	78.81	20.88
	Average	1.094 ± 0.015	24.13 ± 0.44	79.73 ± 4.21	20.33 ± 0.97
2.0	Best	1.085	23.65	75.71	19.42
	Average	1.083 ± 0.019	23.53 ± 0.42	75.41 ± 3.85	19.25 ± 1.38

V_{oc} of 1.05 V, a J_{sc} of 22.88 mA cm^{-2} , and an FF of 71.84%. In contrast, the best PSC based on 1.5 mg mL^{-1} KNFBS agents displayed a PCE of 20.88%, an V_{oc} of 1.10 V, a J_{sc} of 24.18 mA

cm^{-2} , and an FF of 78.81%. The noteworthy increase in J_{sc} was a result of the enlarged perovskite grain size and a raised visible optical absorption of the film.²⁵ As shown in Fig. S2b

and Table S3,[†] the HI values of the reference and target samples were obtained as 0.22 and 0.13, respectively, using the following equation:⁴⁸

$$HI = \frac{PCE_{\text{reverse}} - PCE_{\text{forward}}}{PCE_{\text{reverse}}} \quad (6)$$

The diminished hysteresis effect of the cells can be attributable to the successful suppression of ion migration and reduction of defect density *via* KNFBS addition.

The incident photoelectron conversion efficiency (IPCE) spectrum further verifies the positive impact of KNFBS treatment. As shown in Fig. 2b, the KNFBS-treated sample displays the highest IPCE values, resulting in a raised integrated J_{sc} from 22.69 to 23.95 mA cm^{-2} , in agreement with the measured J_{sc} . Additionally, a steady-state PCE and photocurrent density output were tested to evaluate the operational stability of the pristine and KNFBS-treated devices. As shown in Fig. 2c, the steady-state PCE outputs for the reference and KNFBS-treated

cell under continuous operation with maximum power point (MPP) tracking were 17.10% and 20.14%, respectively. The photocurrent density output for the reference and KNFBS-treated cell were 20.22 and 23.07 mA cm^{-2} , respectively. Moreover, Fig. 2d–g and Table 2 depict the statistical distribution of J_{sc} , V_{oc} , FF and PCE values for the 30 different devices; the 0.5, 1.0, 1.5 and 2 mg mL^{-1} KNFBS added devices deliver average PCEs of 17.16 ± 0.87 , 18.57 ± 1.68 , 19.53 ± 1.3 , 20.33 ± 0.97 and $19.25 \pm 1.38\%$, respectively. The main raised parameters of V_{oc} and FF for the target cell were boosted up to 1.094 ± 0.015 and $79.73 \pm 4.21\%$, respectively, resulting from the enlarged grain size of perovskite.

The effect of KNFBS agents on the morphology of thin films was studied using scanning electron microscopy (SEM). As visualized in Fig. 3a and b, the reference films present some voids, implying a defective film morphology. In contrast, the target films demonstrate compact and homogeneous surface without voids. Fig. 3c and d exhibit the target film with

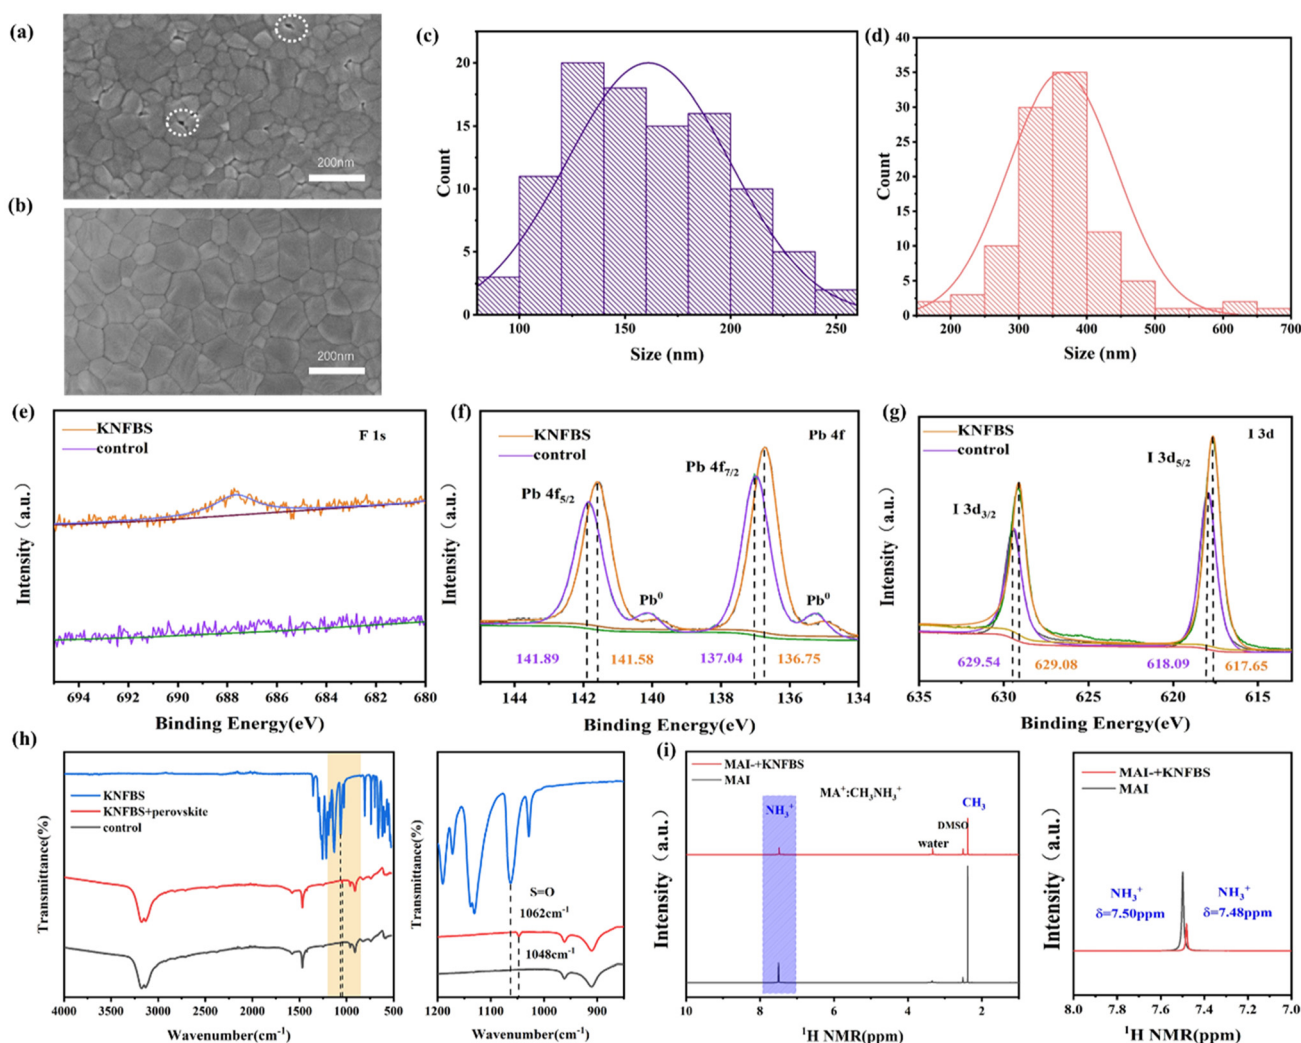


Fig. 3 Top-view SEM images of (a) pristine and (b) KNFBS + perovskite films. Histograms of the grain size of (c) pristine and (d) KNFBS + perovskite films. XPS spectra of control and KNFBS-doped perovskite films: (e) F 1s; (f) Pb 4f and (g) I 3d. (h) FTIR spectra of pure KNFBS passivators, pristine, KNFBS-doped perovskites. (i) NMR spectra of the MAI and mixed MAI + KNFBS in DMSO- d_6 solutions.

larger average grain sizes (~ 360 nm) than the reference one (~ 160 nm), signifying diminished GB areas and grain defects. Beyond that, the released stress at perovskite grains and distorted lattice due to the interaction between KNFBS and perovskite is beneficial for high-quality perovskite films. Besides, atomic force microscopy (AFM) was employed to observe its morphology. As depicted in Fig. S4a and S4b,[†] the surface roughness (RMS) dropped from 12.0 to 9.97 nm after KNFBS treatment. The corresponding 3D diagram manifests that the target film became smoother due to the oriented growth of crystals and diminished defects. The corresponding cross-sectional and top-view SEM images of functional layers (Fig. S5[†]) manifest a thickness of ~ 420 nm for the target film, which is slightly thicker than that of the control film. Meanwhile, a vertical columnar shape was observed in the target layer of Fig. S5b,[†] which was credited for carrier transport along the perpendicular orientation to the ETL/HTL and inhibition of nonradiative carrier recombination.⁴⁹

X-ray photoelectron spectroscopy (XPS) and Fourier transform infrared (FTIR) spectroscopy was conducted to uncover the chemical interaction between KNFBS and perovskite. Fig. 3e and Fig. S6a[†] indicate the incorporation of F atoms into perovskite films. As shown in Fig. 3f, the Pb 4f peaks of 141.9 eV for Pb 4f_{5/2} and 137.04 eV for Pb 4f_{7/2} in the pristine film shift about 0.3 eV toward lower binding energy in the target film (141.6 eV for Pb 4f_{5/2} and 136.75 eV for Pb 4f_{7/2}), due to an increase in the electronic cloud density. This verifies that S=O groups can chelate with the undercoordinated Pb²⁺ ions in the target film.⁵⁰ It is noted that there are two weak signals corresponding to the metallic Pb⁰ cluster in the control film. Generally, the metallic Pb⁰ cluster, along with the I[−] and MA⁺ vacancy defects, are indeed deep-level defects and can exacerbate carrier nonradiative recombination. Thus, the reduced intensity of the Pb⁰ signals verifies that the under-coordinated Pb²⁺ has been effectively suppressed by KNFBS additives. Similarly, a significant shift to lower energy can be observed for the peaks of I 3d_{3/2} and I 3d_{5/2} in Fig. 3g, resulting from the mitigated I[−] vacancies *via* KNFBS passivation in perovskite. The K⁺ metallicity of KNFBS agents at the surface and GBs strongly chelate with I[−] ions and can deactivate the I[−] vacancy defect, thereby resulting in improvement of PCE and diminished *I*-*V* hysteresis.⁵¹ The XPS spectra of N 1s (Fig. S6b[†]) also verifies the interaction between KNFBS and perovskite. These comprehensive results can verify that KNFBS passivators exert preferential interaction with perovskite due to the multiple formation of N-H...F hydrogen bonds and ionic bonds, leading to the improvement of electrical properties and thereby a synergistic passivation effect toward more efficient PSCs.⁵²

As presented in Fig. 3h, the S=O stretching peak of the pristine KNFBS shifted from 1062 cm^{−1} to a lower wavenumber (1048 cm^{−1}) after KNFBS incorporation.⁵³ The decreased vibrational frequency indicates a strong interaction between the sulfonyl groups of KNFBS and the Pb²⁺ ions of perovskite. In addition to XPS results, this result can also imply that the oxygen sites in the anions of KNFBS can serve the role of Lewis

bases, *via* the donation of unpaired electrons to the vacant orbitals of Pb²⁺. Moreover, the strong chemical anchor between KNFBS and perovskite can disassemble the large perovskite colloids in the precursor, leading to the decrease of the perovskite nucleation rate and enlarged perovskite grain size.⁵⁴

To verify the chemical interactions between KNFBS agents and perovskite, nuclear magnetic resonance (NMR) measurements of ¹⁹F and ¹H were implemented by dissolving the powders in deuterated DMSO-*d*₆. As displayed in Fig. S6c,[†] the MAI-KNFBS mixture exhibits an 0.10 ppm increasing chemical shift of the ¹⁹F signal, attributed to the deviation of the N-H electronic cloud to KNFBS and the alteration of the shielding effect, which indicates the chelation of F-ions with MA⁺ and inhibition of the Pb²⁺ vacancy defect (V_{Pb}).⁵⁵ Besides, after the addition of KNFBS into the MAI sample, the ¹H signal of the pristine MAI and MAI-KNFBS mixture was observed to shift from 7.50 to 7.48 ppm (Fig. 3i). The signal belongs to the protons of the NH₃⁺ units of the MA⁺ moiety, which verifies the formation of N-H...F hydrogen bonds. The formation of hydrogen bonds originated from the boosted shielding effect of electrons and increased electron cloud density surrounded by the hydrogen nucleus of NH₃⁺ units.⁵⁶ Thereby, the F, K⁺, and S=O groups in KNFBS agents can be conducive to the stabilization of the perovskite crystal structure with suppressed Pb²⁺ and I[−] vacancies.

Conductive atomic force microscopy (c-AFM) was exerted to visualize not only the distributions of electrical conductivity inner grains and at GBs, but also the traps of the materials in nanoscale, which can elucidate the impact of trap passivation on transport kinetics of charges. As shown in the current images of Fig. 4a and b, the target film reveals a brighter image overall compared with the pristine film, indicating the enhanced conductivity and charge transport of the target film. The overall enhancement in current of the KNFBS-passivated sample is consistent with the more uniform distribution of CPD across the surface (Fig. 5b), and indicates the reduction of trap density at each crystal facet.⁵⁷ The corresponding line profiles of Fig. 4c displays a lower conductance of the pristine film, which is primarily attributable to the charge loss through defect-induced recombination. Interestingly, the control film shows that the current flowing along the GBs is higher than that the grain interior (GI), confirming that GBs play an advantage in charge gathering and transport. Similarly, the significantly brighter GBs of the target films indicates more efficient separation of the photon-generated carrier at the GBs compared with the GI. Thereby, GBs play an important role in transport channels for the carriers.⁵⁸ Due to deactivation of defects including I[−] vacancy and the Pb²⁺ interstitial at GBs, the traps become shallow and the charge mobility is enhanced, which accounts for the boost in photocurrent at GBs compared with that of GIs. Furthermore, the results can also be credited to an offset of band bending between grains and GBs, which can reduce the barrier height and facilitate spatial charge extraction and accumulation, leading to the promotion of carrier transport across GBs.⁵⁹ Moreover, local *I*-*V* properties of inner grains and along GBs were explored to elu-

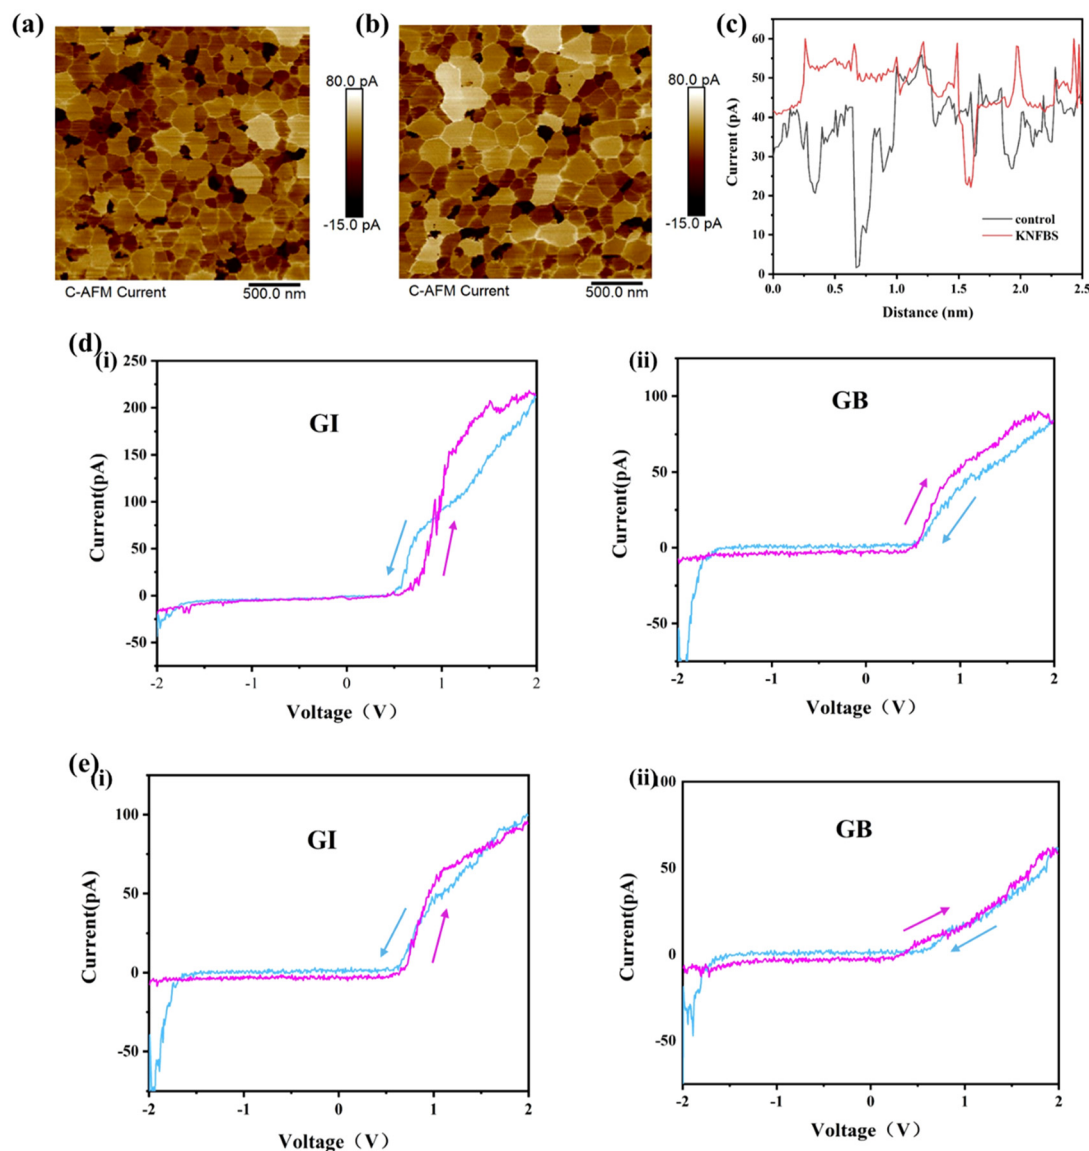


Fig. 4 c-AFM mapping of the currents at perovskite GBs and grains. Current images for (a) the control, (b) KNFBS-doped perovskite films, and (c) current distribution based on random 1D line scanning. Distinct I - V hysteresis at the GI or GBs for (d) the control and (e) KNFBS-doped perovskite films, respectively.

candidate the mechanism of notorious hysteresis in PSCs. As shown in Fig. 4d and e, GBs and GI of the control films exhibit pronounced I - V hysteresis, which can originate from the dominant phenomenon of ion migration and charged defects taking place towards the GI from the GBs where they are rich in defects and dangling bonds.⁶⁰ On the other hand, the target films exhibit diminished I - V hysteresis due to a reduction of ion migration and trap levels, leading to the alteration of electrical properties and the dynamics of charge trapping/de-trapping in GBs.⁶¹

In situ Kelvin probe force microscopy (KPFM) was carried out to monitor electrical properties of the target perovskite films after the doped agents. As shown in the potential mapping of Fig. 5a and b, minimized potential discrepancy

between individual grains and higher surface potential were displayed for KNFBS-treated perovskite films. The evident variations of surface potential in the control film can originate from the high density of the trap state on the surface.⁶² Thus, the alleviated variation of contact potential difference (CPD) in the target film implies that the KNFBS passivator can effectively deactivate surface traps of the sample. The homogenization of CPD between the GB and grains of the target samples demonstrates improvement of the junction properties due to changes of surface traps or band alignments at GBs, which accounts for the reduction of V_{oc} loss in the target devices.⁶³ Moreover, Fig. 5b displays that the overall surface potential of the perovskite film after KNFBS treatment is evidently higher than that of the pristine perovskite sample. The CPD applies

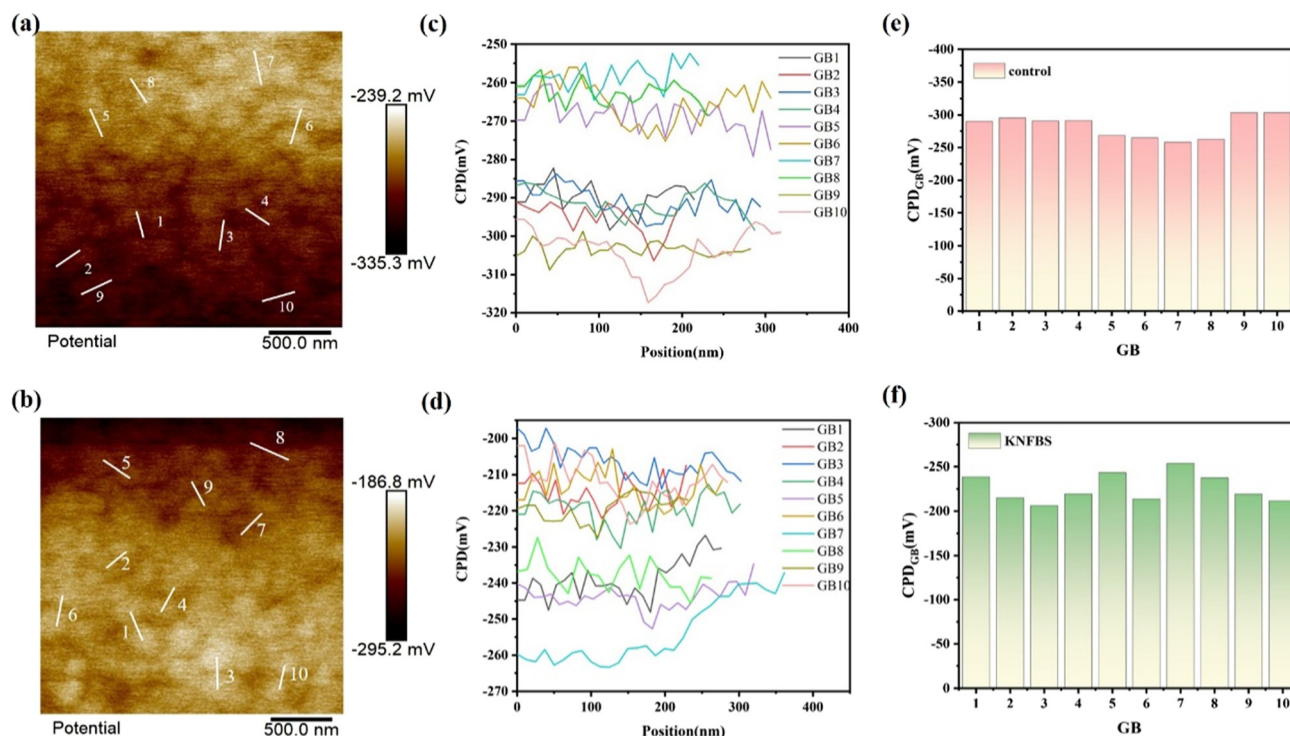


Fig. 5 (a) and (b) Contact potential difference (CPD) image of KPFM mapping. The recorded lines mark the different measured location of GBs. (c) and (d) The profiles based on 1D line scanning of the previous CPD image. (e) and (f) Statistical CPD variation across the GBs based on the corresponding 1D line scanning profiles. The diagrams in the first and second lines are for the control and KNFBS-doped perovskite films, respectively.

to the potential discrepancy between the probe tip and film surface, which is expressed as:

$$\text{CPD} = \frac{\Phi_{\text{tip}} - \Phi_{\text{sample}}}{e} \quad (7)$$

where Φ_{tip} and Φ_{sample} refer to the work function (WF) of the probe tip and the sample, respectively.⁶⁴ Simultaneously, the reduction of the surface potential for the pristine film, which is induced by I^- ion vacancies in grain interiors and GBs, can lead to the lowered Fermi level. The larger CPD value in the KNFBS-treated film (Fig. 5b) indicates a smaller work function and upward energy bending, which is beneficial to more facilitated carrier extraction in the target device. To obtain a more in-depth investigation of the CPD variation between grains, 10 random GBs have been considered for each perovskite film, which correspond to the marked positions in Fig. 5a and b. The line profiles of the marked GBs are shown in Fig. 5c and d. The corresponding histograms of CPD_{GB} in Fig. 5e and f illustrate that the average value of the target film increased by ~ 60 mV. As the value of CPD can measure the magnitude of the built-in electric field, these results indicate a boost driving force for the extraction of photo-induced electrons along GBs.⁶⁵

The molecular structure of the KNFBS agent and multifunctional interaction mechanism between KNFBS and perovskite are illustrated in Fig. S7a† and Fig. 6a, b. First, the sulfur group ($\text{S}=\text{O}$) of KNFBS shows a high passivation potential for Pb_i defects because the high electron density of oxygen atoms on sulfonate anions can effectively bond with Pb^{2+} due to their

Lewis base properties. Secondly, F atoms with increased electronegativity and a smaller ionic radius leads to greater chemical bonding between the halide anions and MA^+ ions *via* the formation of hydrogen-fluorine bonds and ionic bonds,⁶⁶ as illustrated in Fig. S7b.† The interaction between MA^+ of perovskite and F atoms of KNFBS occurs *via* the formation of $\text{MA}\cdots\text{F}$ or the a large molecular dipole.⁶⁷ The introduction of multi-F atoms can exert a synergistic effect due to the *ortho*-position effect and strong electron-withdrawing ability, leading to enhanced negative potential of O atoms.^{68,69} Thirdly, the coordination between K^+ of KNFBS and I^- of perovskite *via* ionic bonds can impede ion migration and phase separation in perovskite films. Some studies verified that K^+ suppresses I^- diffusion, partially *via* blocking the diffusion pathways. Additionally, more energy is required to create an iodide vacancy when K^+ cations are incorporated.⁷⁰

Due to hypersensitivity to oxygen, water, and light radiation^{71–73} for the perovskite materials, the storage long-term stability becomes one of the key parameters to commercialize PSCs. As shown in Fig. 6c, KNFBS-added cells without any encapsulation can hold 82% of the original efficiency after aging for 42 days under ambient conditions ($\text{RH} = 35 \pm 5\%$), which is distinctly superior to the pristine device (58%). The corresponding statistical distribution of aging PCE extracted from 30 cells in Fig. 6d also verified the improved stability of the target devices. As shown in Fig. S8,† FF is more remarkably impacted by humidity exposure compared with V_{oc} and J_{sc} . The decrease in the FF value is over 42% for the reference device.

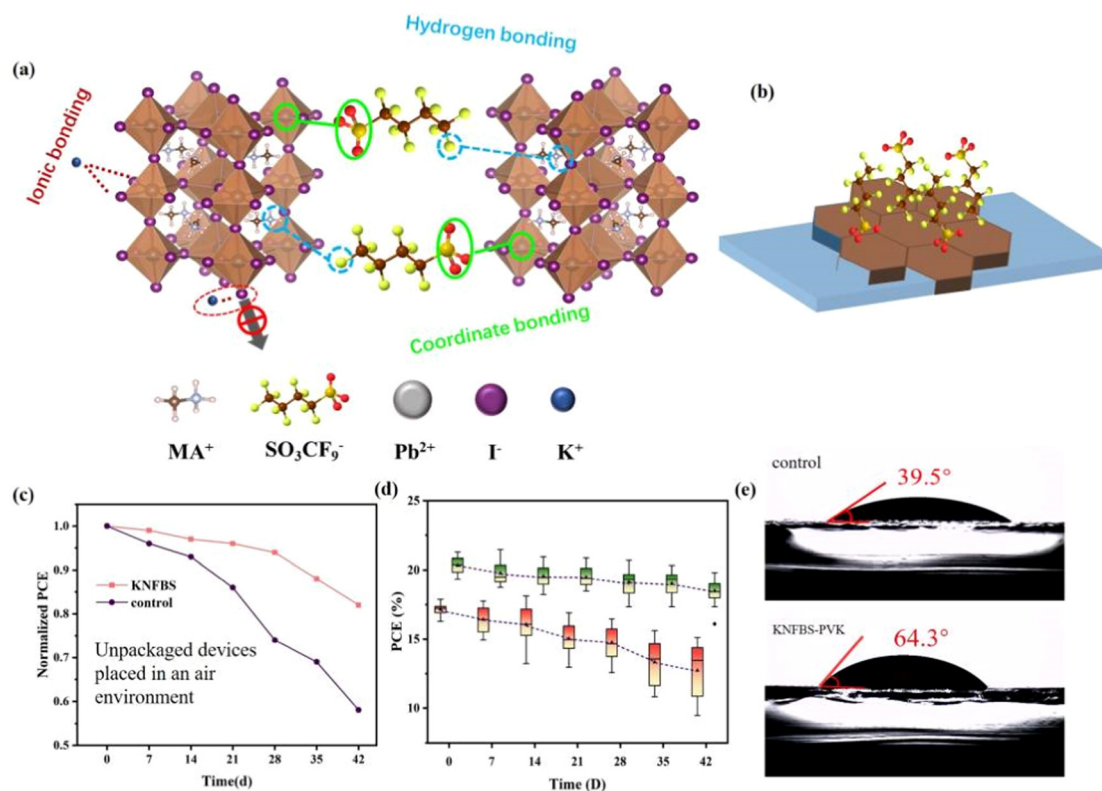


Fig. 6 Schematic of the KNFBS-treated perovskite with multifunctional passivation: (a) chemical interaction between KNFBS molecules and the perovskite, and (b) suppression of ion migration and trap mitigation at GBs. Long-term stability tests of the unencapsulated control and KNFBS-doped devices stored in open air conditions at room temperature with a RH of $35 \pm 5\%$ in the (c) champion devices and (d) corresponding statistical distribution extracted from 30 cells. (e) Water contact angles deposited on control and KNFBS-doped perovskite films.

By. In contrast, the target device can hold more than 70% after 42 d. The improved operation and storage stability of the as-prepared PSCs can primarily result from the better passivation of the KNFBS additives with the multifunctional groups and the facilitated carrier transport due to better matched energy level alignment.

Generally, perovskite degradation was caused by the permeation of moisture and oxygen, which can significantly influence the environmental stability of PSCs and their commercialization. Hydrophobicity of the as-prepared films stored in air was explored using the water contact angles. As presented in Fig. 6e, the contact angles of the pristine and target film were 39.5° and 64.3° , respectively. The significant boosted water contact angle demonstrates that the KNFBS-processed film enhanced the surface hydrophobicity, which can block the water permeation into the photoactive layer. The result can be credited to the water-blocking group of perfluoroalkyl in KNFBS agents and the corresponding close bond with trap sites in perovskite GBs.⁷⁴

3. Conclusion

An organic multifunctional passivator (KNFBS) with anchored chemical bonds was introduced to investigate the passivation

effect on GBs of perovskite film. The cluster of KNFBS agents with a sufficient infiltration force can infiltrate into the GBs of perovskites. The multisite chemical anchors of KNFBS molecules includes the sulfonic acid group chelating with undercoordinated Pb²⁺ ions *via* Lewis acid–base interactions, hydrogen bond between the halogen and MA⁺ ions and ionic bonds between the K⁺ and I⁻. The synergistically designed agents with functional sites of chemical anchors can unambiguously enhance film quality, reduce nonradiative recombination losses and improve carrier-transport kinetics. Additionally, the anchoring bonds can also result in stabilized interface and GBs, as well as minimized I⁻ migration and diffusion. Consequently, the champion device boosts PCE from 17.24% to 20.88% after KNFBS addition, along with a diminished *I*–*V* hysteresis. Additionally, the KNFBS-modified PSCs presented almost no obvious performance degradation after storage in open air conditions at room temperature with a RH of $35 \pm 5\%$, and maintained around 82% of its initial PCE after aging up to 42 d, originated from the protection of hydrophobic KNFBS passivators. We expect that this study will pave the way for the rational design of agent molecules with multiple chemical anchors using only one additive for the unique GB passivation of perovskites, which would provide more strategies for GB engineering and facilitate the transition of photovoltaic perovskite device production from the lab scale to the industrial scale.

4. Experimental section

The materials, preparation process of PSCs, measurements and characterization are shown in the ESI.†

Data availability

We declare that the data behind our research project are reliable and can be accessed by the readers if needed. The data that support the findings of this study are available from the corresponding author upon reasonable request.

Conflicts of interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgements

This research is supported by the National Natural Science Foundation of China (62075053 and 61874156) and the University Synergy Innovation Program of Anhui Province (GXXT-2023-048 and GXXT-2023-067).

References

- 1 M. De Bastiani, V. Larini, R. Montecucco, *et al.*, The leveled cost of electricity from perovskite photovoltaics, *Energy Environ. Sci.*, 2023, **16**(2), 421–429.
- 2 J. Jeong, M. Kim, J. Seo, *et al.*, Pseudo-halide anion engineering for α -FAPbI₃ perovskite solar cells, *Nature*, 2021, **592**(7854), 381–385.
- 3 T.-S. Su, F. T. Eickemeyer, M. A. Hope, *et al.*, Crown Ether Modulation Enables over 23% Efficient Formamidinium-Based Perovskite Solar Cells, *J. Am. Chem. Soc.*, 2020, **142**(47), 19980–19991.
- 4 A. Kojima, K. Teshima, Y. Shirai, *et al.*, Organometal Halide Perovskites as Visible-Light Sensitizers for Photovoltaic Cells, *J. Am. Chem. Soc.*, 2009, **131**(17), 6050–6051.
- 5 National Renewable Energy Laboratory (NREL), Research Cell Efficiency Records, <https://www.nrel.gov/pv/cell-efficiency.html>.
- 6 Y. Cheng and L. Ding, Pushing commercialization of perovskite solar cells by improving their intrinsic stability, *Energy Environ. Sci.*, 2021, **14**(6), 3233–3255.
- 7 M. Stollerfoht, C. M. Wolff, J. A. Márquez, *et al.*, Visualization and suppression of interfacial recombination for high-efficiency large-area pin perovskite solar cells, *Nat. Energy*, 2018, **3**(10), 847–854.
- 8 J. Warby, F. Zu, S. Zeiske, *et al.*, Understanding Performance Limiting Interfacial Recombination in pin Perovskite Solar Cells, *Adv. Energy Mater.*, 2022, **12**(12), 2103567.
- 9 J. Li, R. Xia, W. Qi, *et al.*, Encapsulation of perovskite solar cells for enhanced stability: Structures, materials and characterization, *J. Power Sources*, 2021, **485**, 229313.
- 10 K. Sun, R. Guo, Y. Liang, *et al.*, Morphological Insights into the Degradation of Perovskite Solar Cells under Light and Humidity, *ACS Appl. Mater. Interfaces*, 2023, **15**(25), 30342–30349.
- 11 J. Li, Q. Dong, N. Li, *et al.*, Direct Evidence of Ion Diffusion for the Silver-Electrode-Induced Thermal Degradation of Inverted Perovskite Solar Cells, *Adv. Energy Mater.*, 2017, **7**(14), 1602922.
- 12 Y. Yuan and J. Huang, Ion Migration in Organometal Trihalide Perovskite and Its Impact on Photovoltaic Efficiency and Stability, *Acc. Chem. Res.*, 2016, **49**(2), 286–293.
- 13 F. Gao, Y. Zhao, X. Zhang, *et al.*, Recent Progresses on Defect Passivation toward Efficient Perovskite Solar Cells, *Adv. Energy Mater.*, 2019, **10**(13), 1902650.
- 14 J. Si, H. Sha, B. Qu, *et al.*, Synergistic effect of surface active agent in defect passivation by for ambient air-synthesized halide perovskite solar cells, *J. Power Sources*, 2022, **524**, 231038.
- 15 S. M. Park, M. Wei, J. Xu, *et al.*, Engineering ligand reactivity enables high-temperature operation of stable perovskite solar cells, *Science*, 2023, **381**(6654), 209–215.
- 16 H. Jiang, C. Wei, J. Wang, *et al.*, A novel chain-like conjugated donor- π -acceptor molecular additive for highly efficient and stable perovskite solar cells, *Chem. Eng. J.*, 2024, **490**, 151778.
- 17 S. Zhou, S. Fu, C. Wang, *et al.*, Aspartate all-in-one doping strategy enables efficient all-perovskite tandems, *Nature*, 2023, **624**(7990), 69–73.
- 18 H. Zhang, L. Pfeifer, S. M. Zakeeruddin, *et al.*, Tailoring passivators for highly efficient and stable perovskite solar cells, *Nat. Rev. Chem.*, 2023, **7**(9), 632–652.
- 19 S. Cao, L. Wang, X. She, *et al.*, Enhanced Efficiency and Stability of Inverted CsPbI₂Br Perovskite Solar Cells via Fluorinated Organic Ammonium Salt Surface Passivation, *Langmuir*, 2024, **40**, 3715–3724.
- 20 F. Khan, M. T. Khan, S. Rehman, *et al.*, Analysis of electrical parameters of p-i-n perovskites solar cells during passivation via N-doped graphene quantum dots, *Surf. Interfaces*, 2022, **31**, 102066.
- 21 L. Liu, S. Huang, Y. Lu, *et al.*, Grain-Boundary “Patches” by In Situ Conversion to Enhance Perovskite Solar Cells Stability, *Adv. Mater.*, 2018, **30**(29), 1800544.
- 22 Z. Liu, Z. Su, B. Yu, *et al.*, Biomaterial Improves the Stability of Perovskite Solar Cells by Passivating Defects and Inhibiting Ion Migration, *ACS Appl. Mater. Interfaces*, 2024, **16**(24), 31218–31227.
- 23 H. Wen, Y. Guo, T. Yin, *et al.*, Tailoring Defect Passivation for Efficient and Stable Perovskite Solar Cells via an Ionic Liquid Additive, *ACS Appl. Energy Mater.*, 2024, **7**(8), 3137–3144.

- 24 C. A. Aranda, A. O. Alvarez, V. S. Chivrony, *et al.*, Overcoming ionic migration in perovskite solar cells through alkali metals, *Joule*, 2024, **8**(1), 241–254.
- 25 X. Chang, H. Tang, Z. Xie, *et al.*, Imidazole-Based Ionic Liquid Engineering for Perovskite Solar Cells with High Efficiency and Excellent Stability, *ACS Appl. Mater. Interfaces*, 2024, **16**(26), 33917–33927.
- 26 J. Fang, L. Wang, Z. Chen, *et al.*, Sulfonic Acid Functionalized Ionic Liquids for Defect Passivation via Molecular Interactions for High-Quality Perovskite Films and Stable Solar Cells, *ACS Appl. Mater. Interfaces*, 2024, **16**, 23443–23451.
- 27 J. Shang, L. Zhou, J. Zhang, *et al.*, Dual-Passivation Strategy with Escaped Thiocyanate and Sturdy Chloride toward Large-Scale Wide-Band-Gap Perovskite Modules, *J. Phys. Chem. C*, 2024, **128**(14), 6080–6088.
- 28 R. Su, Z. Xu, J. Wu, *et al.*, Dielectric screening in perovskite photovoltaics, *Nat. Commun.*, 2021, **12**(1), 2479.
- 29 Z. Liang, Y. Zhang, H. Xu, *et al.*, Homogenizing out-of-plane cation composition in perovskite solar cells, *Nature*, 2023, **624**(7992), 557–563.
- 30 Q. Tan, Z. Li, G. Luo, *et al.*, Inverted perovskite solar cells using dimethylacridine-based dopants, *Nature*, 2023, **620**(7974), 545–551.
- 31 C. M. Sutter-Fella, D. W. Miller, Q. P. Ngo, *et al.*, Band Tailing and Deep Defect States in $\text{CH}_3\text{NH}_3\text{Pb}(\text{I}_{1-x}\text{Br}_x)_3$ Perovskites As Revealed by Sub-Bandgap Photocurrent, *ACS Energy Lett.*, 2017, **2**(3), 709–715.
- 32 X. Zhou, X. Luan, L. Zhang, *et al.*, Dual Optimization of Bulk and Interface via the Synergistic Effect of Ligand Anchoring and Hole Transport Dopant Enables 23.28% Efficiency Inverted Perovskite Solar Cells, *ACS Nano*, 2023, **17**(4), 3776–3785.
- 33 Q. Cao, Y. Zhang, X. Pu, *et al.*, Surface passivation by multi-functional carbon dots toward highly efficient and stable inverted perovskite solar cells, *J. Energy Chem.*, 2023, **86**, 9–15.
- 34 J. Zhuang, P. Mao, Y. Luan, *et al.*, Rubidium Fluoride Modified SnO_2 for Planar n-i-p Perovskite Solar Cells, *Adv. Funct. Mater.*, 2021, **31**(17), 2010385.
- 35 A. Carbone, B. K. Kotowska and D. Kotowski, Space-Charge-Limited Current Fluctuations in Organic Semiconductors, *Phys. Rev. Lett.*, 2005, **95**(23), 236601.
- 36 S.-H. Lee, S. Jeong, S. Seo, *et al.*, Acid Dissociation Constant: A Criterion for Selecting Passivation Agents in Perovskite Solar Cells, *ACS Energy Lett.*, 2021, 1612–1621.
- 37 X. Chen, L. Ai, H. Ji, *et al.*, Silane Doping for Efficient Flexible Perovskite Solar Cells with Improved Defect Passivation and Device Stability, *ACS Appl. Mater. Interfaces*, 2024, **16**(37), 49293–49304.
- 38 Y. Su, J. Yang, G. Liu, *et al.*, Acetic Acid-Assisted Synergistic Modulation of Crystallization Kinetics and Inhibition of Sn^{2+} Oxidation in Tin-Based Perovskite Solar Cells, *Adv. Funct. Mater.*, 2021, **32**(12), 210963.
- 39 W. Tress, M. Yavari, K. Domanski, *et al.*, Interpretation and evolution of open-circuit voltage, recombination, ideality factor and subgap defect states during reversible light-soaking and irreversible degradation of perovskite solar cells, *Energy Environ. Sci.*, 2018, **11**(1), 151–165.
- 40 M. Fischer, K. Tvingstedt, A. Baumann, *et al.*, Doping Profile in Planar Hybrid Perovskite Solar Cells Identifying Mobile Ions, *ACS Appl. Energy Mater.*, 2018, **1**, 5129–5134.
- 41 L. Gao, Y. Zhao, Y. Chang, *et al.*, *In situ* compensation for thermal strain by phase transformation strain in all-inorganic perovskite solar cells, *Chem. Eng. J.*, 2023, **469**, 143881.
- 42 B. Roose, K. Dey, M. R. Fitzsimmons, *et al.*, Electrochemical Impedance Spectroscopy of All-Perovskite Tandem Solar Cells, *ACS Energy Lett.*, 2024, **9**(2), 442–453.
- 43 Y. Liu, S. Ji, S. Li, *et al.*, Study on hole-transport-material-free planar $\text{TiO}_2/\text{CH}_3\text{NH}_3\text{PbI}_3$ heterojunction solar cells: the simplest configuration of a working perovskite solar cell, *J. Mater. Chem. A*, 2015, **3**(28), 14902–14909.
- 44 W. Xiang, E. Cronk, J. Wall, *et al.*, Double Perovskite Interlayer Stabilized Highly Efficient Perovskite Solar Cells, *ACS Appl. Mater. Interfaces*, 2024, **16**(34), 44988–44996.
- 45 M. T. Neukom, A. Schiller, S. Züfle, *et al.*, Consistent Device Simulation Model Describing Perovskite Solar Cells in Steady-State, Transient, and Frequency Domain, *ACS Appl. Mater. Interfaces*, 2019, **11**(26), 23320–23328.
- 46 E. C. Smith, C. L. C. Ellis, H. Javai, *et al.*, Interplay between Ion Transport, Applied Bias, and Degradation under Illumination in Hybrid Perovskite p-i-n Devices, *J. Phys. Chem. C*, 2018, **122**(25), 13986–13994.
- 47 A. V. Ivanishchev, A. V. Ushakov, I. A. Ivanishcheva, *et al.*, Structural and electrochemical study of fast Li diffusion in $\text{Li}_3\text{V}_2(\text{PO}_4)_3$ -based electrode material, *Electrochim. Acta*, 2017, **230**, 479–491.
- 48 W. Li, M. U. Rothmann, Y. Zhu, *et al.*, The critical role of composition-dependent intragrain planar defects in the performance of $\text{MA}_{1-x}\text{FA}_x\text{PbI}_3$ perovskite solar cells, *Nat. Energy*, 2021, **6**(6), 624–632.
- 49 Y. Li, D. Yao, Z. Tang, *et al.*, SnO_2 -Perovskite Interface Engineering Based on Bifacial Passivation via Multifunctional N-(2-Acetamido)-2-aminoethanesulfonic Acid toward Efficient and Stable Solar Cells, *ACS Appl. Mater. Interfaces*, 2024, **16**(7), 9388–9399.
- 50 H. Zheng, W. Wu, H. Xu, *et al.*, Self-Additive Low-Dimensional Ruddlesden-Popper Perovskite by the Incorporation of Glycine Hydrochloride for High-Performance and Stable Solar Cells, *Adv. Funct. Mater.*, 2020, **30**(15), 2000034.
- 51 M. Abdi-Jalebi, Z. Andaji-Garmaroudi, S. Cacovich, *et al.*, Maximizing and stabilizing luminescence from halide perovskites with potassium passivation, *Nature*, 2018, **555**(7697), 497–501.
- 52 K. Zou, Q. Li, J. Fan, *et al.*, Pyridine Derivatives' Surface Passivation Enables Efficient and Stable Carbon-Based Perovskite Solar Cells, *ACS Mater. Lett.*, 2022, **4**(6), 1101–1111.
- 53 D. R. Scheuing and J. G. Weers, A Fourier transform infrared spectroscopic study of dodecyltrimethylammonium

- chloride/sodium dodecyl sulfate surfactant mixtures, *Langmuir*, 1990, **6**(3), 665–671.
- 54 S. Tan, J. Shi, B. Yu, *et al.*, Inorganic Ammonium Halide Additive Strategy for Highly Efficient and Stable CsPbI₃ Perovskite Solar Cells, *Adv. Funct. Mater.*, 2021, **31**(21), 201083.
 - 55 C. Tian, B. Li, Y. Rui, *et al.*, In Situ Polymerizing Internal Encapsulation Strategy Enables Stable Perovskite Solar Cells toward Lead Leakage Suppression, *Adv. Funct. Mater.*, 2023, **33**(41), 2302270.
 - 56 M.-H. Li, S. Wang, X. Ma, *et al.*, Hydrogen-bonding-facilitated dimethylammonium extraction for stable and efficient CsPbI₃ solar cells with environmentally benign processing, *Joule*, 2023, **7**(11), 2595–2608.
 - 57 S. Y. Leblebici, L. Leppert, Y. Li, *et al.*, Facet-dependent photovoltaic efficiency variations in single grains of hybrid halide perovskite, *Nat. Energy*, 2016, **1**(8), 16093.
 - 58 Y. Shi, E. Rojas-Gatjens, J. Wang, *et al.*, (3-Aminopropyl)trimethoxysilane Surface Passivation Improves Perovskite Solar Cell Performance by Reducing Surface Recombination Velocity, *ACS Energy Lett.*, 2022, **7**(11), 4081–4088.
 - 59 H. Liu, J. Wang, Y. Qu, *et al.*, Defect Management and Ion Infiltration Barrier Enable High-Performance Perovskite Solar Cells, *ACS Energy Lett.*, 2024, **9**(6), 2790–2799.
 - 60 D. Seol, A. Jeong, M. H. Han, *et al.*, Origin of Hysteresis in CH₃NH₃PbI₃ Perovskite Thin Films, *Adv. Funct. Mater.*, 2017, **27**(37), 1701924.
 - 61 W. Kaiser, K. Hussain, A. Singh, *et al.*, Defect formation and healing at grain boundaries in lead-halide perovskites, *J. Mater. Chem. A*, 2022, **10**(46), 24854–24865.
 - 62 Q. Jiang, J. Tong, Y. Xian, *et al.*, Surface reaction for efficient and stable inverted perovskite solar cells, *Nature*, 2022, **611**(7935), 278–283.
 - 63 H. Yang, R. Li, S. Gong, *et al.*, Multidentate Chelation Achieves Bilateral Passivation toward Efficient and Stable Perovskite Solar Cells with Minimized Energy Losses, *Nano Lett.*, 2023, **23**(18), 8610–8619.
 - 64 M. Lorenzoni and F. Pérez-Murano, Conductive Atomic Force Microscopy for Nanolithography Based on Local Anodic Oxidation [M], *Conduct. At. Force Microsc.*, 2017, 211–223.
 - 65 M. I. Saidaminov, K. Williams, M. Wei, *et al.*, Multi-cation perovskites prevent carrier reflection from grain surfaces, *Nat. Mater.*, 2020, **19**(4), 412–418.
 - 66 N. Li, S. Tao, Y. Chen, *et al.*, Cation and anion immobilization through chemical bonding enhancement with fluorides for stable halide perovskite solar cells, *Nat. Energy*, 2019, **4**(5), 408–415.
 - 67 C. Liu, S. Liu, Y. Wang, *et al.*, Improving the Performance of Perovskite Solar Cells via a Novel Additive of N,1-Fluoroformamidinium Iodide with Electron-Withdrawing Fluorine Group, *Adv. Funct. Mater.*, 2021, **31**(18), 2010603.
 - 68 Y. Wang, S. Ye, Z. Sun, *et al.*, Multifunctional Regioisomeric Passivation Strategy for Fabricating Self-Driving, High Detectivity All-Inorganic Perovskite Photodetectors, *ACS Appl. Mater. Interfaces*, 2023, **15**(50), 59005–59015.
 - 69 D. J. Yoo, Q. Liu, O. Cohen, *et al.*, Rational Design of Fluorinated Electrolytes for Low Temperature Lithium-Ion Batteries, *Adv. Energy Mater.*, 2023, **13**(20), 2204182.
 - 70 J. Cao, S. X. Tao, P. A. Bobbert, *et al.*, Interstitial Occupancy by Extrinsic Alkali Cations in Perovskites and Its Impact on Ion Migration, *Adv. Mater.*, 2018, **30**(26), 1707350.
 - 71 Q. Lai, R. Zhuang, K. Zhang, *et al.*, A Multifunctional Liquid Crystal as Hole Transport Layer Additive Enhances Efficiency and Stability of Perovskite Solar Cells, *Angew. Chem., Int. Ed.*, 2023, **62**(31), e202305670.
 - 72 S. Ruan, M.-A. Surmiak, Y. Ruan, *et al.*, Light induced degradation in mixed-halide perovskites, *J. Mater. Chem. C*, 2019, **7**(30), 9326–9334.
 - 73 J. Zhou, Z. Liu, P. Yu, *et al.*, Modulation of perovskite degradation with multiple-barrier for light-heat stable perovskite solar cells, *Nat. Commun.*, 2023, **14**(1), 6120.
 - 74 X. Chen, H. Ran, Y. Zhao, *et al.*, Regulating Functional Groups to Construct a Mild Passivator Enhancing the Efficiency and Stability of Carbon-Based Perovskite Solar Cells, *ACS Appl. Mater. Interfaces*, 2024, **16**(37), 49293–49304.