

Cite this: *J. Mater. Chem. A*, 2025, 13, 12216

# Controlled oxidation of V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> hollow nanospheres as photocathodes for photo-rechargeable zinc ion batteries with an ultrahigh capacity enhancement†

Hongran Yang,<sup>a</sup> Shilei Wu,<sup>a</sup> Akeshe Manimendra Badalge,<sup>c</sup> Xinyu Li,<sup>c</sup> Qianjin Wang,<sup>ab</sup> Yu Lin Zhong<sup>bc</sup> and Ting Zhu<sup>id\*ab</sup>

Photo-charging batteries are emerging as a new battery technology for large-scale energy storage systems. However, their specific capacity, cycling stability, and light efficiency have reached a bottleneck due to low light-absorption capability, sluggish separation and migration of photoinduced charge carriers, and severe photocorrosion. Herein, hollow nanospheres composed of divanadium pentaoxide/vanadium dioxide (V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub>) are constructed to broaden light harvesting and improve the redox activity of photo-rechargeable zinc ion batteries (ZIBs). Due to an *in situ* chemical reaction, V<sub>2</sub>O<sub>5</sub> and VO<sub>2</sub> are intimately connected to form a V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> heterojunction, thus facilitating the separation and migration of photoinduced charge carriers. As a result, this V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> heterojunction demonstrated a maximum surface photovoltage (SPV) of 25.73 mV, resulting in an ultrahigh specific capacity of 785.6 mA h g<sup>-1</sup> at 200 mA g<sup>-1</sup> through a light-discharging process. This delivers a high light enhancement of 77.8% with a power conversion efficiency (PCE) of 4.3%. In addition, ZIBs show promising stability under light irradiation, where a high retention of 53.1% can be achieved even at high current density of 1000 mA g<sup>-1</sup> after 4000 cycles. This work has pushed forward ZIB technology into a green and sustainable path that can utilize solar energy to promote electrochemical energy storage.

Received 19th January 2025  
Accepted 17th March 2025

DOI: 10.1039/d5ta00517e

rsc.li/materials-a

## 1. Introduction

Solar energy is a green and sustainable energy source that plays an increasing role in energy storage and conversion applications, such as lithium ion batteries (LIBs), zinc ion batteries (ZIBs), supercapacitors (SCs), metal air batteries (MABs), and electrocatalysis (ECs).<sup>1–3</sup> In these energy systems, photo-energy can be harvested using a semiconductor, and the resulting photoinduced charge carriers facilitate charge transfer and accumulation for subsequent storage and conversion. In early 2012, Wang *et al.* demonstrated an integrated power pack composed of a LIB cell and a dye sensitized solar cell (DSSC) employing light-sensitive TiO<sub>2</sub> nanotubes; the LIB cell can be directly charged by the DSSC-based solar cell with an energy conversion and storage efficiency of 0.82%.<sup>4</sup> Subsequent research by Dai *et al.* developed this photo-charging mode by

connecting the LIBs to perovskite solar cells, where the photo-electric conversion and storage efficiency was significantly increased to 7.80%.<sup>5</sup> However, the as-reported photo-assisted battery packages contained two separated parts for light-harvesting and charge storage, inevitably leading to a large energy loss and high manufacturing costs.

To alleviate these problems, researchers have proposed the exploration of integrated photo-batteries that can simultaneously harvest light and store charge within a single device.<sup>6</sup> This integration strategy endows a higher potential to provide compact battery devices with lighter weight, further reducing the manufacturing costs, and improving the storage and conversion efficiency.<sup>7</sup> For this optimized type of photo-electric conversion, dual-functional electrode materials should be carefully designed and synthesized to balance the photoelectric properties and electrochemical activity.<sup>8</sup> Typical semiconductive materials such as TiO<sub>2</sub>,<sup>9–11</sup> Cu<sub>2</sub>O,<sup>12</sup> V<sub>2</sub>O<sub>5</sub>,<sup>13</sup> Fe<sub>2</sub>O<sub>3</sub>,<sup>14</sup> and C<sub>3</sub>N<sub>4</sub> (ref. 15) with various structures have been employed to serve as dual-functional electrodes for fabrication of the photo-assisted batteries. Recently, Jiang *et al.* described an integrated LIB electrode composed of TiO<sub>2</sub>/SnO<sub>2</sub> heterojunctions, where the photogenerated electrons of TiO<sub>2</sub> can be transferred to SnO<sub>2</sub> under light illumination to promote the redox reaction during the charging process. As a result, the specific capacity of the photo-LIBs increased from

<sup>a</sup>School of Physics and Electronic Information, Yunnan Normal University, 768 Juxian Street, Kunming 650500, China. E-mail: zhut0002@ynnu.edu.cn

<sup>b</sup>Yunnan Key Laboratory of Optoelectronic Information Technology, School of Physics and Electronic Information, Yunnan Normal University, Kunming 650500, China

<sup>c</sup>School of Environment and Science, Griffith University, Nathan, QLD 4111, Australia

† Electronic supplementary information (ESI) available: Additional SEM, XRD, UV-vis, electrochemical and calculation data, optical images, etc. of the materials and photo-batteries. See DOI: <https://doi.org/10.1039/d5ta00517e>

1.91 to 3.47 mA h cm<sup>-2</sup> at 5 mA cm<sup>-2</sup>, corresponding to a considerable capacity enhancement of 81.6%.<sup>16</sup> Meanwhile, Yang S. Y. *et al.* photoinduced Cu<sup>+</sup>/Cu<sup>2+</sup> round-trip valence change in CuO electrode to promote the lithium storage reaction, and the discharge specific capacity can be increased from 539.29 to 580.70 mA h g<sup>-1</sup> with the assistance of light energy.<sup>17</sup> The increasing reports of introducing light energy into energy storage devices also triggered intensive attention of photo-charging aqueous zinc ion batteries (AZIBs) because AZIBs are considered much cheaper and safer than LIBs while still offering considerable energy density.<sup>18</sup> Pioneering work by Volder *et al.* reported a V<sub>2</sub>O<sub>5</sub> nanofiber-based photoactive cathode, by which the gravimetric capacity of the fabricated ZIBs can be elevated from 190 to 370 mA h g<sup>-1</sup> with photo-conversion efficiencies of ~1.2%.<sup>19</sup> After that, the sample group prepared VO<sub>2</sub> nanorods as dual-functional electrodes for photo-rechargeable AZIBs, and the rate performances can be largely improved with light (photo-conversion efficiency of 0.18% at 455 nm).<sup>20</sup> Despite high capacitance enhancements with improved light efficiencies of photo-batteries (including ZIBs), the detailed mechanisms of photo-assisted enhancement, the separation and migration of photoinduced charge carriers, and capacity decay incurred by photocorrosion are not fully understood. Therefore, it is highly desirable to explore the inter-relationship between the photoelectric property and ZIB performance to understand the charge transfer occurring in the photo-assisted charge-discharge process.

In this work, photocathodes composed of V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> hollow nanospheres are easily constructed to achieve a homogeneous heterojunction that broadens light harvesting and simultaneously enhances redox activity. By compositional and structural design, the surface photovoltage (SPV) of these hollow nanospheres can be optimized to be as high as 30 mV. As a result, the fabricated AZIBs using these V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> hollow nanospheres can deliver a specific capacity of 785.6 mA h g<sup>-1</sup> at 200 mA g<sup>-1</sup>, which is much higher than that obtained without light at the same current density (441.8 mA h g<sup>-1</sup>), corresponding to a light enhancement of 77.8%. In addition, a capacity retention of 53.1% was maintained even at a high current density of 1000 mA g<sup>-1</sup> for charge-discharge under a full-time test under illumination. Finally, the light power conversion efficiency (PCE) based on a single-wavelength light source (365 nm) was 4.3%. This work demonstrates a designed synthesis of dual-functional V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> photocathodes for AZIBs by tuning the chemical compositions and hollow structures. It exhibits a promising application in the next-generation photo-rechargeable ZIBs.

## 2. Experimental section

### 2.1 Synthesis of vanadium-based precursors

In a typical reaction, 5.34 g of oxalic acid (C<sub>2</sub>H<sub>2</sub>O<sub>4</sub>·2H<sub>2</sub>O) was dissolved in 150 mL of deionized (DI) water to form a homogeneous solution. Then, 3 g of commercial V<sub>2</sub>O<sub>5</sub> particles was added to the solution to form a yellow suspension under magnetic stirring. The sample was heated in a water bath at 60 °C. Under magnetic stirring, the solution turned from green to blue, which indicated the reduction of V<sup>5+</sup> to V<sup>4+</sup> by the formation of vanadium-based precursor. Finally, the product was rinsed with

DI water, collected through centrifugation, dried at 75 °C for 2 days, then ground in a mortar to obtain the precursor powder.

### 2.2 Preparation of VO<sub>2</sub> hollow nanospheres

In a typical procedure, 50 mg of precursor powder was added to a 60 mL solution mixture of methanol and water (4 : 1 vol%). After magnetic stirring for 10 min, the resultant light blue translucent solution was transferred into a 100 mL Teflon-lined stainless-steel autoclave, then heated in an electric air-flow oven at 200 °C for 24 h. After cooling down naturally, the obtained black product was harvested by centrifugation, washed with DI water and ethanol several times before drying overnight at 70 °C.

### 2.3 Construction of V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> mixed hollow nanospheres

The as-prepared VO<sub>2</sub> nanospheres were annealed at 300 °C for 5 min in a muffle furnace with a heating rate of 2 °C min<sup>-1</sup> and cooled down naturally before sample collection.

### 2.4 Material characterization

The morphology and structure were examined by scanning electron microscope (SEM) using a Quanta FEG 250 instrument and transmission electron microscopy (TEM) with high-resolution transmission electron microscopy (HRTEM) with a Tecnai G2 F20 instrument. Thermal gravimetric analysis (TGA) was performed using a thermal tube furnace (Hefei Kejing, GSL-1100X-S-TGA) within a temperature range of 20–300 °C. The chemical states of all the elements in the samples were detected by X-ray photoelectron spectroscopy (XPS) using an ESCALAB250Xi instrument (Thermo Fisher-VG Scientific), and the results were calibrated with a C 1s peak at 284.6 eV. X-ray diffraction was conducted by an X-ray diffractometer (XRD, Rigaku D/max 2500) with Cu K $\alpha$  radiation ( $\lambda = 1.5406 \text{ \AA}$ ) to examine the crystal phases of the samples. Ultraviolet-visible diffuse reflectance spectroscopy (UV-vis DRS) was employed to determine the light adsorption property of the samples using a Shimadzu UV-3600 UV-vis spectrophotometer.

### 2.5 Preparation of photocathodes

First, the active material, carbon nanotubes, and polyvinylidene fluoride (PVDF 5130) were mixed in a ratio of 7 : 2 : 1 (actual weights of 35 mg, 10 mg, and 5 mg, respectively). Then, 1.5 mL of *N*-methylpyrrolidone (NMP) was added, and the mixture was sonicated for 2 h, with the ultrasonic machine paused every 20 minutes for agitation. After that, 100  $\mu$ L of the mixture was dropped onto a carbon paper with a loading area of 0.36  $\pi$  cm<sup>2</sup> (which had been cleaned with alcohol and deionized water, followed by 5 minutes of plasma cleaning). The carbon paper with the loaded material was then transferred to a vacuum oven and dried at 60 °C for 12 h to obtain the final working electrode. The mass loading was approximately 1.8 mg cm<sup>-2</sup>.

### 2.6 Fabrication of ZIB full cells

First, an 8 mm round hole was punched in the center of a coin battery (CR2032) shell, and a thin ring of UV adhesive was applied around the edge of the hole. A transparent conductive

ITO was adhered to the punched area to seal the hole window closely using a UV lamp, but allowing light to pass through. A piece of Zn foil anode ( $R = 16$  mm, thickness = 0.05 mm),  $V_2O_5/VO_2$  photocathode, and glass microfiber separator (Whatman GF/D A6, 16 mm) were assembled in this CR2032-type coin cell with 120  $\mu$ L of 3 M  $Zn(CF_3SO_3)_2$  aqueous electrolyte.

### 2.7 Electrochemical measurements

All the cyclic voltammetry (CV) cycles, voltage–time ( $I-t$ ) tests, electrochemical impedance spectroscopy (EIS) measurements, rate performances, and long-cycle tests of the ZIBs were conducted using an IVIUM electrochemical workstation (Vertex. C. EIS). Impedance tests were performed within a frequency range of 100 kHz to 0.01 Hz, with a voltage amplitude of 0.01 mV. Galvanostatic charge/discharge (GCCD) curves were obtained using a Neware battery testing system. For the light irradiation measurements of the battery cells, a single-wavelength LED ( $\lambda = 365$  nm) was used as the light source. The distance between the light and the battery cell is around 10 cm, and the power of the LED light is  $\sim 100$  mW  $cm^{-2}$ . To ensure long-term electrochemical measurements under illumination, a small fan was placed on one side of the battery to maintain a constant temperature during measurements.

### 2.8 Theoretical calculation

All computational work was completed in the Cambridge Sequential Total Energy Package (CASTEP), which is a computational software package based on density-functional theory (DFT).

The CASTEP can provide atomic-scale descriptions of a wide variety of materials, including studies of surface bonding structures, density of states, optical properties, *etc.* The generalized gradient approximation (GGA) function was used to characterize electron interactions using the Perdew–Burke–Ernzerhof (PBE) approximation and the projector augmented wave (PAW) method was used to characterize electron/ion interactions in atoms. Pure phase  $VO_2$ ,  $V_2O_5$ , and  $V_2O_5/VO_2$  were established, and the space groups of  $VO_2$  and  $V_2O_5$  were  $P2_1/C$  and  $Pm\bar{3}n$ , respectively. The  $V_2O_5/VO_2$  was obtained by cleaving the  $VO_2$  and  $V_2O_5$  along the (001) direction. Additionally, the Monkhorst–Pack K-points for  $VO_2$  and  $V_2O_5$  and  $V_2O_5/VO_2$  were set to  $3 \times 3 \times 3$  and  $2 \times 2 \times 1$ , respectively, and the cutoff energy was 450 eV. In addition, we added a 25 Å vacuum layer to avoid the effect of periodicity in the  $z$ -axis direction. The valence electron configuration of each atom is [V]  $3d^34s^2$  and [O]  $2s^22p^6$ . For structural optimization, the maximum force convergence accuracy and energy convergence accuracy were taken to be  $5 \times 10^{-2}$  eV  $\text{\AA}^{-1}$  and  $1.0 \times 10^{-5}$  eV per atom, respectively.

## 3. Results and discussion

The synthetic method for the preparation of  $V_2O_5/VO_2$  hollow nanospheres employed a simple solution/annealing strategy (Fig. 1a). First, vanadium-based precursor ( $VOC_2O_4$ ) was synthesized by a stirring and drying process using commercial  $V_2O_5$  particles (as shown by the SEM images in Fig. S1†) as

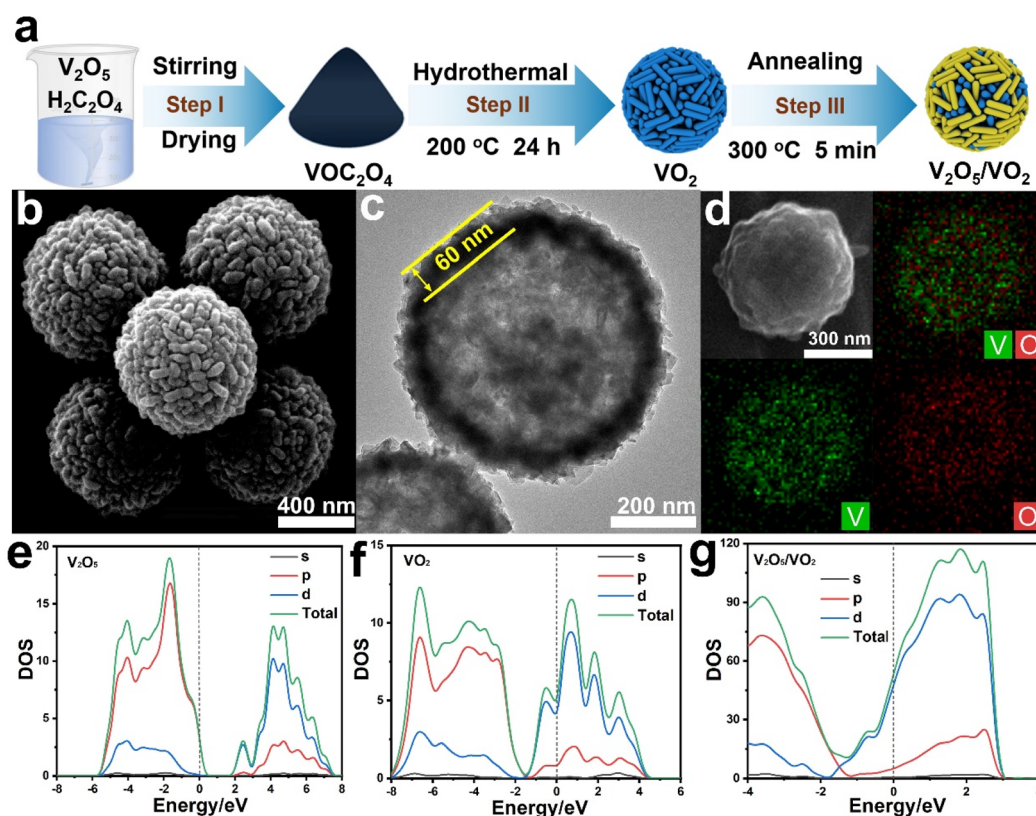


Fig. 1 Synthetic scheme (a), SEM (b), TEM (c) and elemental mapping (d) results of the  $V_2O_5/VO_2$  hollow nanospheres, and density of states of  $V_2O_5$  (e),  $VO_2$  (f), and  $V_2O_5/VO_2$  (g).

a vanadium source (step I). Next, the as-prepared  $\text{VOCl}_2$  precursor was transformed into  $\text{VO}_2$  hollow nanospheres *via* a hydrothermal synthesis with a reaction temperature of 200 °C for 24 h (step II). Finally, the collected  $\text{VO}_2$  nanospheres (SEM and XRD shown in Fig. S2 and S3,† respectively) were dried at 60 °C for 12 h and subsequently annealed at 300 °C in air for 5 min to derive the mixed  $\text{V}_2\text{O}_5/\text{VO}_2$  hollow nanospheres (step III).

In our experiments,  $\text{VO}_2$  could be completely converted to  $\text{V}_2\text{O}_5$  if the annealing time was extended to 30 min. Some of the  $\text{VO}_2$  of the spheres was *in situ* oxidized to  $\text{V}_2\text{O}_5$ , leading to an intimate contact of these two components. However, the well-defined spheres with the hollow structures can be well maintained after heat treatment, which was confirmed from the SEM image (Fig. 1b). The as-obtained  $\text{V}_2\text{O}_5/\text{VO}_2$  spheres have an average diameter of  $\sim 650$  nm and are composed of nanosized building units. The structural details with the hollow feature of these nanospheres were further examined by TEM (Fig. 1c). The individual sphere shows a highly porous and hollow texture with a shell thickness of  $\sim 60$  nm. Elemental mappings were also conducted to examine the elemental distributions of the sphere. V and O are homogeneously interspersed (Fig. 1d), showing the formation of vanadium oxides within the spheres. Theoretical calculations were performed to study the density of states (DOS) of the as-prepared materials. The CASTEP software was used for optimization, and the optimized models are displayed in Fig. S4.† Next, we calculated the band gap of the  $\text{VO}_2$  and  $\text{V}_2\text{O}_5$  pure phases, as well as the  $\text{V}_2\text{O}_5/\text{VO}_2$  heterojunction. The band gap of  $\text{V}_2\text{O}_5$  is 2.018 eV, while the band gap of  $\text{VO}_2$  is 0.165 eV (Fig. S5†). This suggests that  $\text{V}_2\text{O}_5$  displays a wider bandgap with poor conductivity, whereas  $\text{VO}_2$  may exhibit a stronger conductivity. However, the combination of the wide bandgap of  $\text{V}_2\text{O}_5$  and the metal-insulator transition

characteristics of  $\text{VO}_2$  results in  $\text{V}_2\text{O}_5/\text{VO}_2$  exhibiting a recombination phenomenon of conduction and valence bands in heterojunction systems that displays metallic characteristics.

The DOS is a significant physical quantity that characterizes the distribution of electronic energy within a material. The DOS of  $\text{VO}_2$ ,  $\text{V}_2\text{O}_5$ , and  $\text{V}_2\text{O}_5/\text{VO}_2$  is illustrated in Fig. 1e–g, with the horizontal axis representing energy. The Fermi level ( $E_f$ ) is situated at 0 eV, with the valence band positioned to the left and the conduction band to the right of the Fermi level. In Fig. 1e and f, the valence band is predominantly constituted by O 2p orbitals, whereas the conduction band is primarily comprised of V 3d orbitals. Pure phase  $\text{VO}_2$  and  $\text{V}_2\text{O}_5$  exhibit certain electronic states at the Fermi level. However,  $\text{VO}_2$  displays a greater number of these states, which results in stronger conductivity properties. Fig. 1g illustrates a substantial concentration of states (free electrons) appearing at the conduction band, which can move freely and improve its electrical properties. In summary, the bandgap and DOS of heterojunctions undergo substantial alterations due to the emergence of interface states. The  $\text{V}_2\text{O}_5/\text{VO}_2$  heterojunction structures exhibit enhanced interface charge transfer performance and broader light absorption capabilities.

To determine the ratio of  $\text{VO}_2$  in the  $\text{V}_2\text{O}_5/\text{VO}_2$  spheres, TGA was conducted in a tube furnace with a temperature range from 20 to 300 °C. First, the sample powder was heated from 20 to 300 °C with a heating rate of 2 °C  $\text{min}^{-1}$  and maintained at 300 °C for 5 min for partial oxidation, followed by another 30 min for complete oxidation (Fig. 2a). As a result, part of the  $\text{VO}_2$  was oxidized to  $\text{V}_2\text{O}_5$  during the annealing by the ratios decreasing, and the ratio of  $\text{VO}_2$  in the final  $\text{V}_2\text{O}_5/\text{VO}_2$  sample was determined to be  $\sim 20\%$  (annealed at 300 °C for 5 min, indicated by the red dot).

Then, the crystal phases of the as-obtained  $\text{V}_2\text{O}_5/\text{VO}_2$  spheres were examined by XRD (Fig. 2b). All the identified XRD peaks

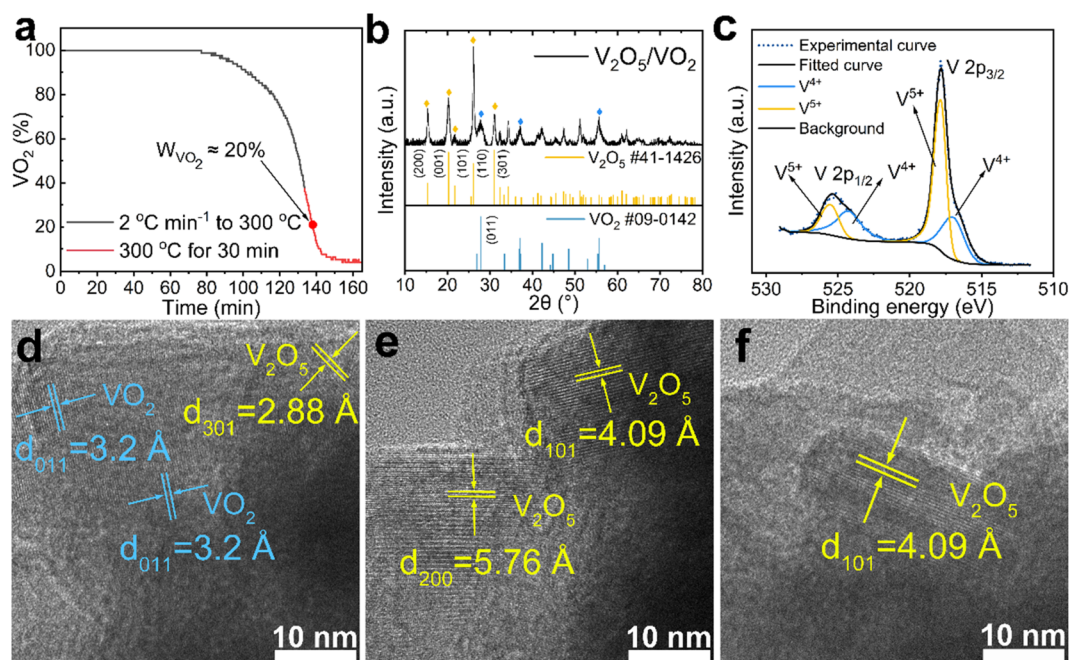


Fig. 2 TGA curve (a), XRD pattern (b), XPS spectra (c), and HR-TEM images (d–f) of the  $\text{V}_2\text{O}_5/\text{VO}_2$  hollow nanospheres.

can be assigned to mixed phases of  $V_2O_5$  (JCPDS 41-1426)<sup>21</sup> and  $VO_2$  (JCPDS 09-0142).<sup>22</sup> In addition, the chemical states of the V elements were determined by XPS (Fig. 2c). The binding energies of 517.6 and 525.5 eV can be assigned to V 2p<sub>3/2</sub> and V 2p<sub>1/2</sub> of V<sup>5+</sup>, respectively, while the binding energies of 517.2 and 524.7 eV can be attributed to V 2p<sub>3/2</sub> and V 2p<sub>1/2</sub> of V<sup>4+</sup>, respectively.<sup>23,24</sup> This XPS result confirmed the co-existence of  $V_2O_5$  and  $VO_2$  in the as-constructed nanospheres. To further detect the structural details of the nanospheres, HR-TEM images were obtained to reveal the lattice information of these  $V_2O_5/VO_2$  nanospheres. The inner shell of the hollow sphere reveals the presence of  $V_2O_5$  and  $VO_2$  (Fig. 2d). Specifically, the identified lattice distance of 2.88 Å can be assigned to  $V_2O_5$  (301), while the lattice distances of 3.2 Å is attributed to  $VO_2$  (011). The outer structure of the sphere is more easily oxidized during the annealing process due to better contact with air. Thus, it is reasonable to find that only  $V_2O_5$  is identified in the outer layer of the sphere, which can be confirmed by the presence of (101) and (200) with lattice distances of 4.09 and 5.76 Å, respectively (Fig. 2e). In addition, only  $V_2O_5$  (101) is found at the outmost nanosheets structure, suggesting that the annealing process can facilitate the evolution of  $V_2O_5$  with a specific lattice structure (Fig. 2f). To investigate the light properties of the as-prepared  $VO_x$ -based materials, UV-vis analysis was conducted for the  $V_2O_5$ ,  $VO_2$ , and  $V_2O_5/VO_2$  samples between 300–800 nm (Fig. S6†). The intermediate  $VO_2$  sample displayed a narrow light adsorption within 400 nm, corresponding to a calculated bandgap of ~2.95 eV. Meanwhile, the adsorption range of the  $V_2O_5$  sample can be broadened to ~600 nm with a narrower bandgap of 2.06 eV. The bandgap of

the material was further narrowed to 1.75 eV with the formation of the  $V_2O_5/VO_2$  heterostructure, which exhibited good light adsorption between 600–800 nm. The as-prepared  $V_2O_5/VO_2$  hollow spheres may present good light harvesting properties for electrochemical Zn<sup>2+</sup> storage.<sup>25</sup>

Due to the best light adsorption of the  $V_2O_5/VO_2$  sample, Kelvin probe force microscope (KPFM) was employed to further detect the geometry and photoelectric property by a line scanning mode. Fig. 3a and b show the two-dimensional and three-dimensional KPFM images, respectively, of the  $V_2O_5/VO_2$  nanospheres, where the brightness in the images indicates the height of the surface structure. Fig. 3c shows the actual height distribution map of the area indicated by the white line in Fig. 3a. A maximum height of 640 nm was detected, which is very close to the average particle size (650 nm) by the SEM and TEM observations. The surface potentials of the nanospheres with/without light irradiation were measured and compared (Fig. 3d and e), in which higher surface potentials can be obtained with light irradiation compared to those without light. The surface potentials of the selected  $V_2O_5/VO_2$  particles 1–3 by line scanning with/without light irradiation were plotted in Fig. 3f, and the SPV for particles 1–3 were 25.73, 22.07, and 24.59 mV, respectively.

The maximum specific SPV based on the diameter of the nanospheres (~650 nm) was calculated to be ~39.5 kV m<sup>-1</sup>. A high SPV usually indicates an efficient separation and migration of charge carriers.<sup>26</sup> Before the light charge-discharge measurements, the photocurrent response was evaluated for the as-fabricated ZIB cells ( $V_2O_5/VO_2/CNTs//Zn$ , using 3 M Zn(CF<sub>3</sub>SO<sub>3</sub>)<sub>2</sub> aqueous solution as the electrolyte). A steady

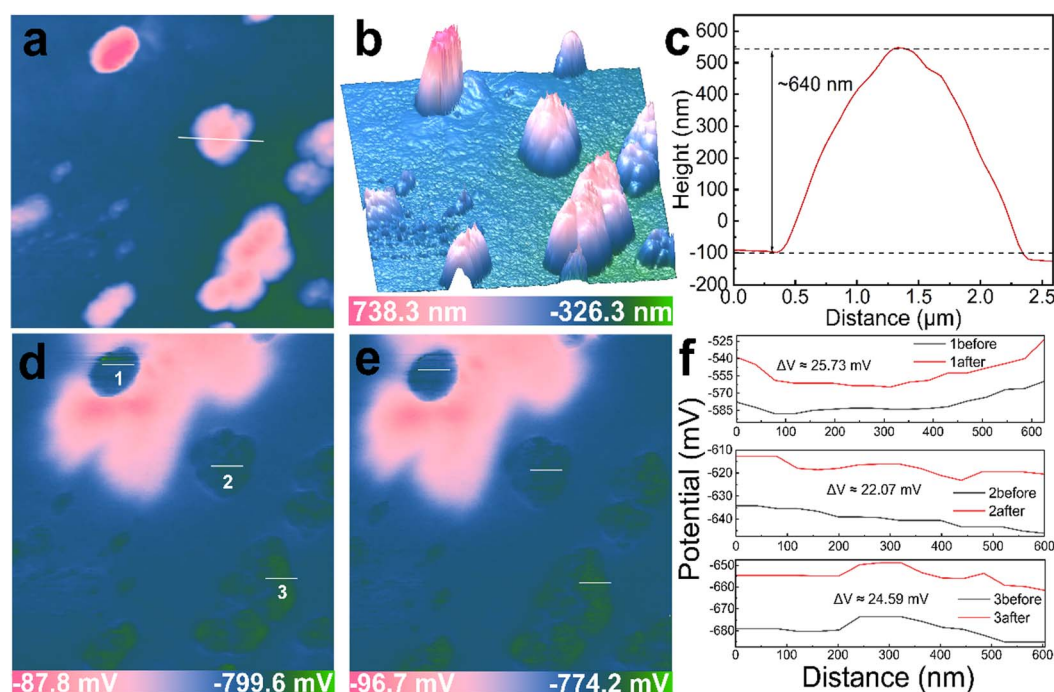


Fig. 3 Two-dimensional (a) and three-dimensional (b) KPFM images, actual height distribution map of the white line section (c), the corresponding KPFM surface potential images without (d) and with (e) light irradiation, and the comparisons of surface potentials with/without light irradiation of the as-prepared  $V_2O_5/VO_2$  nanospheres (f).

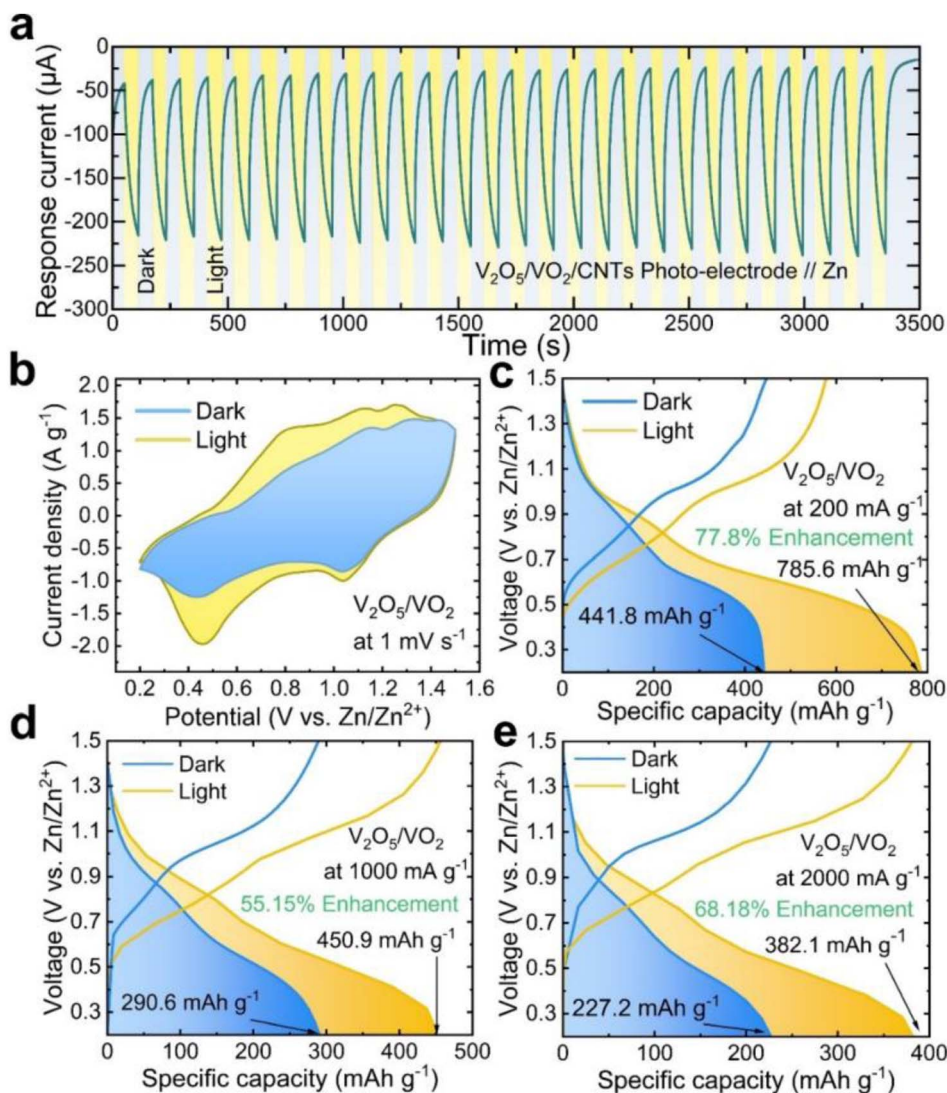


Fig. 4 Photocurrent response (a), CV curves obtained within a potential window of 0.2–1.5 V under dark and light conditions (b), charge–discharge curves obtained at current densities of  $200\text{ mA g}^{-1}$  (c),  $1000\text{ mA g}^{-1}$  (d), and  $2000\text{ mA g}^{-1}$  (e) under dark and light conditions of the as-fabricated ZIBs cells employing  $V_2O_5/VO_2$  as photocathodes.

responsive current is observed under light irradiation (Fig. 4a), with the current value significantly increasing from  $-48\text{ }\mu A$  in the dark to  $\sim 220\text{ }\mu A$  in the light, revealing an enhancement of over 4.5 times. Next, the as-prepared  $V_2O_5/VO_2$  materials were used as photoelectrodes for the fabrication of modified CR2032 coin cells (Fig. S7a and b<sup>†</sup>), in which a transparent PET film was used to envelop the circular window but allow the light to pass through. Next, CV measurements were conducted for the ZIB cell at a scan rate of  $1\text{ mV s}^{-1}$  under dark and light conditions, respectively (Fig. 4b). Two pairs of peaks were observed in the dark ( $1.14/1.04\text{ V}$ ,  $0.79/0.45\text{ V}$ ), while positively shifted peaks were obtained under light ( $1.15/1.05\text{ V}$ ,  $0.8/0.47\text{ V}$ ).

Remarkably, a larger CV area can be seen under light conditions compared to that obtained in the dark, revealing the light-enhanced redox reaction occurring in the CV process. Charge–discharge curves performed at various current densities ( $200\text{--}2000\text{ mA g}^{-1}$ ) were displayed in Fig. 4c–e, where high

enhancements of 55.15–77.8% were calculated under light conditions. The specific discharge capacity at  $200\text{ mA g}^{-1}$  was calculated to be  $441.8\text{ mA h g}^{-1}$  in the dark and can be increased to  $785.6\text{ mA h g}^{-1}$  in the light, delivering the highest enhancement of 77.8%. When the current density was increased to  $1000\text{ mA g}^{-1}$ , the specific capacities under dark and light conditions were reduced to  $290.6$  and  $450.9\text{ mA h g}^{-1}$ , respectively. A high specific capacity of  $382.1\text{ mA h g}^{-1}$  can be maintained at a current density of  $2000\text{ mA g}^{-1}$ , revealing an enhancement of 68.18%. This unusually higher light enhancement at  $2000\text{ mA g}^{-1}$  compared with  $1000\text{ mA g}^{-1}$  could be caused by the activation of cathode materials under light irradiation. To evaluate the photothermal effect of the materials, the PET film was colored black with a marker pen (Fig. S7c<sup>†</sup>). At a current density of  $1000\text{ mA g}^{-1}$ , the specific discharge capacities obtained in the dark and light were calculated to be  $364$  and  $367\text{ mA h g}^{-1}$ , respectively (Fig. S7d<sup>†</sup>), which reveals

that the photothermal effect only contributed a capacity enhancement of 0.82%. At  $1000 \text{ mA g}^{-1}$ , the specific capacities of the intermediate  $\text{VO}_2$  cathodes in the dark and light are  $437$  and  $503 \text{ mA h g}^{-1}$ , respectively (Fig. S8†), showing a light enhancement of 15.1%. At a higher current density of  $2000 \text{ mA g}^{-1}$ , the capacity can be enhanced by 18% from  $376$  to  $445 \text{ mA h g}^{-1}$ . These results suggest that the  $\text{V}_2\text{O}_5$  component in the  $\text{V}_2\text{O}_5/\text{VO}_2$  mixed oxide likely enhances the photoelectric conversion due to its superior light absorption capability, thereby additionally contributing to the overall capacity under illumination.<sup>27</sup> The photo-energy enhancement mechanism in this  $\text{V}_2\text{O}_5/\text{VO}_2$ -based AZIB is primarily achieved by photo-induced charge transfer and accelerated ion diffusion under illumination, where the light serves as an external driving force

that promotes pseudocapacitive surface reactions ( $\text{V}^{5+} \rightarrow \text{V}^{4+}$ ) and bulk ion diffusion ( $\text{Zn}^{2+}/\text{H}^+$  intercalation).<sup>28</sup> In addition, the  $\text{V}_2\text{O}_5/\text{VO}_2$  heterostructure forms a built-in electric field at the interface, which reduces the recombination rate of the electrons and holes. This may have enhanced the efficient migration of charged ions, including the intercalation/de-intercalation of Zn ions.

To further evaluate the rate performances of the as-fabricated photo-ZIBs, the discharge specific capacities were obtained at various current densities in the dark and light conditions (Fig. 5a). At a relatively low current density of  $200 \text{ mA g}^{-1}$ , the capacity increase in the light was calculated as  $\sim 27.2\%$  (from  $440$  to  $560 \text{ mA h g}^{-1}$ , 40–45<sup>th</sup> cycles) and can be increased to  $\sim 121\%$  (from  $230$  to  $510 \text{ mA h g}^{-1}$ ) at a higher

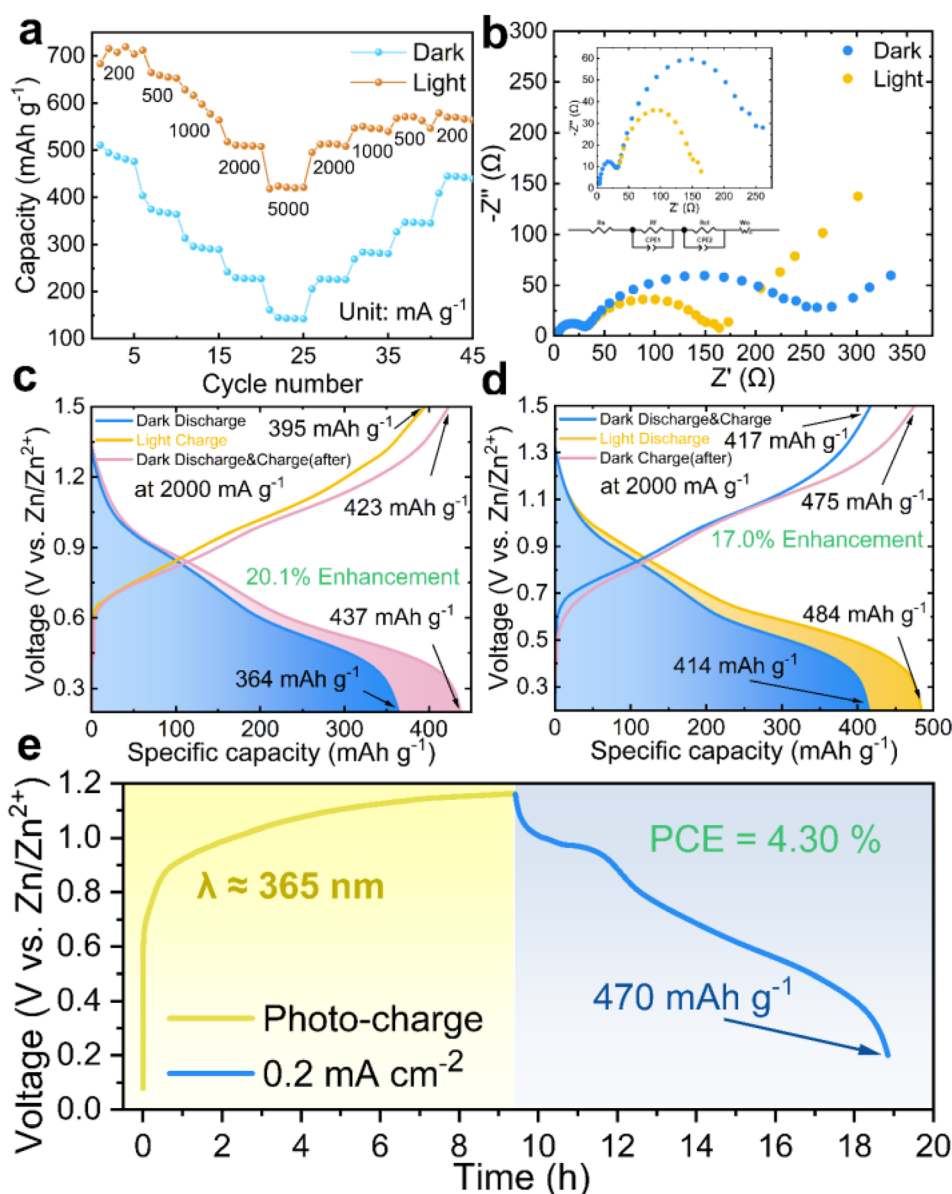


Fig. 5 Rate performances (a), EIS spectra (b), light charge and dark discharge curves obtained at a current density of  $2000 \text{ mA g}^{-1}$  (c), dark charge and light discharge curves obtained at  $2000 \text{ mA g}^{-1}$  using a full-spectrum Xe lamp (d), and the light charge and dark discharge curve obtained using a single-wavelength LED light of  $\sim 365 \text{ nm}$  of the as-fabricated photo-ZIBs (e).

current density of  $2000 \text{ mA g}^{-1}$ . Illumination can result in a much higher capacity increase of  $\sim 180\%$  (from  $150$  to  $420 \text{ mA h g}^{-1}$ ) at a very high current density of  $5000 \text{ mA g}^{-1}$ . These rate performances show that the photo-ZIBs prepared herein can deliver better light enhancement at higher current densities, which suggests a great potential for fast-charging of next-generation ZIBs. The EIS plots of the photo-ZIBs clearly show that the contact resistance can be largely reduced upon light irradiation (Fig. 5b). To further investigate the role of light energy in the charge–discharge process, charge/discharge curves under the light and dark conditions were obtained and compared (Fig. 5c). At a current density of  $2000 \text{ mA g}^{-1}$ , the specific capacity during light charging was calculated as  $395 \text{ mA h g}^{-1}$  and was maintained at  $364 \text{ mA h g}^{-1}$  during the dark discharge process. After this round, the photo-battery was re-charged in the dark, and the specific capacity was increased to  $423 \text{ mA h g}^{-1}$ , which could be caused by the activation of  $\text{V}_2\text{O}_5/\text{VO}_2$  photocathode materials. In addition, the specific capacity obtained by the subsequent dark discharge was calculated as  $437 \text{ mA h g}^{-1}$ , exhibiting an enhancement of  $\sim 20.1\%$  versus the first-run discharge capacity. Next, the same battery was recharged in the dark at the same current density and delivered a slightly lower capacity of  $417 \text{ mA h g}^{-1}$  with a discharge capacity of  $414 \text{ mA h g}^{-1}$ , respectively (Fig. 5d). After this run, the battery was recharged in the dark again, which has demonstrated a higher capacity of  $475 \text{ mA h g}^{-1}$ . The re-charged battery was then allowed to discharge in the light, which can

deliver a much higher capacity of  $484 \text{ mA h g}^{-1}$ , corresponding to a light enhancement of  $\sim 17\%$ . These results show that light provides additional charge carriers to promote the specific capacities and activates the photocathodes to further improve Zn ion storage.<sup>29</sup> Fig. 5e shows an additional light charge and dark discharge test of the battery at  $0.2 \text{ mA cm}^{-2}$  to facilitate the calculation of light power efficiency using an LED as the light source (UV-vis spectra, Fig. S6†).

The discharge capacity can be calculated as  $470 \text{ mA h g}^{-1}$  with a high light PCE of  $4.3\%$ . Cycling stability is considered very important to ZIBs and the prolonged cycling tests were conducted for the photo-ZIBs. First, CV measurements of the photo-batteries employing  $\text{V}_2\text{O}_5$ ,  $\text{VO}_2$ , and  $\text{V}_2\text{O}_5/\text{VO}_2$  photocathodes were performed at  $1 \text{ mV s}^{-1}$  in the light (Fig. 6a), where much higher redox peaks can be observed for the  $\text{V}_2\text{O}_5/\text{VO}_2$ -based battery. The  $\text{V}_2\text{O}_5/\text{VO}_2$ -based photo-battery was first cycled in the dark at  $200 \text{ mA g}^{-1}$ , in which the specific capacity increased sharply to  $\sim 590 \text{ mA h g}^{-1}$ , and then gradually decreased to  $\sim 423 \text{ mA h g}^{-1}$  after 500 cycles, corresponding to a steady capacity retention of  $84.6\%$  (Fig. 6b).

Next, the same battery cell was cycled at a higher current density of  $1000 \text{ mA g}^{-1}$  in the light to show a potential in fast charge–discharge. The initial discharge capacity was  $313.5 \text{ mA h g}^{-1}$  and degraded gradually to  $166.5 \text{ mA h g}^{-1}$  after 4000 cycles, exhibiting a capacity retention of  $53.1\%$  and a Coulomb efficiency of  $\sim 100\%$  (Fig. 6c). The capacity drop during this long-term cycling test may be partly caused by photo

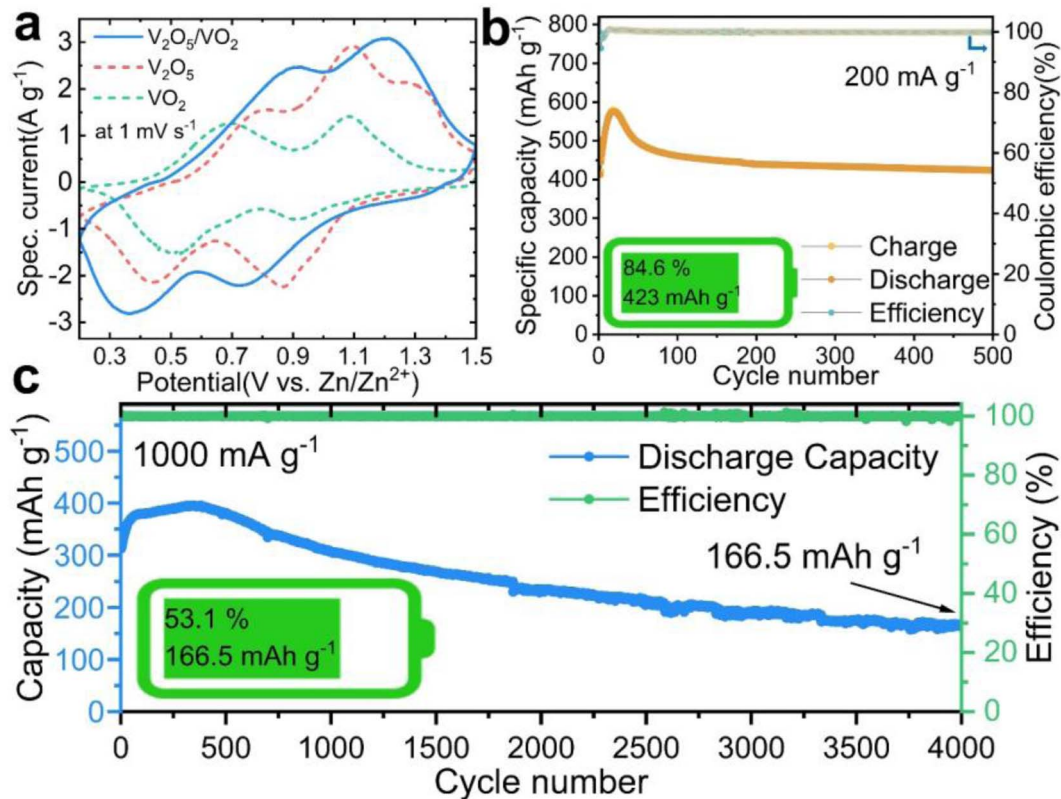


Fig. 6 CV curves of  $\text{V}_2\text{O}_5$ ,  $\text{VO}_2$ , and  $\text{V}_2\text{O}_5/\text{VO}_2$  photocathode-based ZIBs at a scan rate of  $1 \text{ mV s}^{-1}$  in light (a) and the cycling performances of  $\text{V}_2\text{O}_5/\text{VO}_2$  photocathode-based ZIBs conducted at current densities of  $200 \text{ mA g}^{-1}$  (b) and  $1000 \text{ mA g}^{-1}$  (c) of the  $\text{V}_2\text{O}_5/\text{VO}_2$  photocathode-based ZIBs in the light condition.



corrosion of the cathode materials,<sup>30</sup> because the light was applied throughout the cycling tests. In addition, the loss of Zn anode is another important reason for the capacity decay. Thus, the morphology and composition of the cathode after cycling tests were analyzed. After cycling for 500 times at a current density of 5 A g<sup>-1</sup>, the battery cell was disassembled to collect the cathode material for SEM and EDX characterization (Fig. S9†). Zn particles can be found on the surface of the cathode, suggesting the formation of “dead zinc”, which could be another explanation for the capacity decay upon cycling. The F and S elements in mapping are originated from the Zn(CF<sub>3</sub>-SO<sub>3</sub>)<sub>2</sub> electrolyte. Consequently, electrolyte additives such as nanocellulose can be used to suppress the Zn dendrites to enhance the long-term performance, and further reduce the photocorrosion of V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> by surface coating of a thin carbon layer. However, the formation of the V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> heterojunction herein could be favorable to enhance the charge separation and migration, thus reducing hole accumulation at the electrode surface.<sup>31</sup> This can minimize the oxidation of VO<sub>2</sub>, possibly mitigating the long-term photocorrosion. Finally, The ZIB performances of this work are comparable with those of photo-batteries (including ZIBs and LIBs) reported previously (Table S1, ESI†). To study the crystal and chemical states changes of V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> electrodes during the repeated intercalation and de-intercalation of zinc ions, *ex situ* XRD and XPS analysis were performed for the cathodes (loaded onto carbon cloth, CC) at different charge–discharge states of the ZIB cells. First, XRD patterns of the pristine CC and V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> loaded CC (Fig. S10a†) showed no impurities, with only peaks of V<sub>2</sub>O<sub>5</sub> and CC. Next, the V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> loaded CC was cycled and discharged to 1 V and 0.2 V at the 10<sup>th</sup> cycle (10D1.0 and 10D0.2, Fig. S10b†), respectively. XRD peaks for ZnV<sub>3</sub>O<sub>8</sub> can be clearly distinguished, revealing the partial occupation of V sites by Zn. Subsequently, the cells were re-charged to 1 V and 1.5 V again, where XRD peaks for V<sub>3</sub>O<sub>7</sub> and VO(OH)<sub>2</sub> were detected for the cathodes, showing good reversible properties for Zn intercalation and de-intercalation. In addition, further XPS results show that the intensity for V<sup>5+</sup> was remarkably reduced when V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> loaded CC was charged to 1.5 V and then discharged to 0.2 V (Fig. S10c†). The intensity for Zn was distinctly increased during this charge–discharge process but without any peak shift of binding energies (Fig. S10d†), verifying the intercalation and de-intercalation of Zn within the V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> cathodes. To evaluate the structural stability of the cathode materials, SEM/EDX and XRD data of the materials were obtained and displayed after 4000 cycles (Fig. S11†). Compared to the dark condition, more VO(OH)<sub>2</sub> was formed within the cathode under light conditions (Fig. S11a†), revealing an increased intercalation of hydrated Zn ions under light irradiation. In addition, nanosheet-like layered structures were found (Fig. S11b–d†), which could be due to the formation of hydroxylated species, such as VO(OH)<sub>2</sub>.

## 4. Conclusions

Hollow nanospheres composed of V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> mixed oxides were prepared to broaden light harvesting and improve the redox activity of the photocathodes for photo-rechargeable ZIBs. The

hollow feature of the spheres was verified by SEM and TEM characterization, while the light sensitivity was confirmed by UV-vis spectra. The highlight of the as-prepared V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> nanospheres is the considerable SPV value, which was examined and confirmed by the KPFM images collected under illuminated and dark conditions. As a result, the photo-batteries employing these V<sub>2</sub>O<sub>5</sub>/VO<sub>2</sub> hollow nanospheres can realize a maximum specific capacity of 785.6 mA h g<sup>-1</sup> at a current density of 200 mA g<sup>-1</sup> in the light, delivering a capacity enhancement of 77.8% with a light PCE of 4.3%. Finally, the photo-battery can present a high cyclic retention of 53.1% even at a high current density of 1000 mA g<sup>-1</sup> after 4000 cycles during the light charge–discharge process, which indicates a high potential for next-generation photo-rechargeable zinc ion batteries. Importantly, the as-described photo-assisted charging feature may bring great changes in the battery technology by expanding the application scenarios. For example, the portable electronic devices can be automatically charged outdoors or in a solar environment, reducing reliance on traditional chargers.

## Data availability

The data supporting this article have been included as part of the ESI.†

## Author contributions

H. R. Yang carried out the experiments, collected, and analyzed the data; S. L. Wu and Q. J. Wang assisted the data collection and analysis; T. Zhu conceived the research idea, supervised the project, analyzed the data and wrote the manuscript; A. M. Badalge revised the manuscript. X. Y. Li and Y. L. Zhong provided important discussions and revised the manuscript.

## Conflicts of interest

The authors declare no conflict of interest.

## Acknowledgements

This work was financially supported by the National Natural Science Foundation of China (grant no. 52263028), and Yunnan Fundamental Research Projects (grant no. 202301AT070059).

## References

- 1 Y.-X. Tan, X. Zhang, J. Lin and Y. Wang, *Energy Environ. Sci.*, 2023, **16**, 2432–2447.
- 2 M. R. Yang, D. H. Wang, Y. H. Ling, X. N. Guo and W. H. Chen, *Adv. Funct. Mater.*, 2024, 2410398.
- 3 H. M. Liu, X. R. Gao, Y. T. Lou, H. K. Liu, S. X. Dou, Z. C. Bai and N. N. Wang, *Adv. Energy Mater.*, 2024, 2402381.
- 4 W. Guo, X. Xue, S. Wang, C. Lin and Z. L. Wang, *Nano Lett.*, 2012, **12**, 2520–2523.
- 5 J. Xu, Y. Chen and L. Dai, *Nat. Commun.*, 2015, **6**, 8103.
- 6 A. Paoletta, C. Faure, G. Bertoni, S. Marras, A. Guerfi, A. Darwiche, P. Hovington, B. Commarieu, Z. Wang,

- M. Prato, M. Colombo, S. Monaco, W. Zhu, Z. Feng, A. Vijh, C. George, G. P. Demopoulos, M. Armand and K. Zaghbi, *Nat. Commun.*, 2017, **8**, 14643.
- 7 J. Lv, J. Xie, A. G. A. Mohamed, X. Zhang and Y. Wang, *Chem. Soc. Rev.*, 2022, **51**, 1511–1528.
- 8 A. Gouder, F. Podjaski, A. Jiménez-Solano, J. Kröger, Y. Wang and B. V. Lotsch, *Energy Environ. Sci.*, 2023, **16**, 1520–1530.
- 9 J. H. Li, Y. Q. Zhang, Y. Y. Mao, Y. Y. Zhao, D. X. Kan, K. Zhu, S. L. Chou, X. T. Zhang, C. L. Zhu, J. Ren and Y. J. Chen, *Angew. Chem., Int. Ed.*, 2023, **62**, e202303056.
- 10 W. Yan, J. Wang, Q. Hu, J. J. Fu, M. K. Albolqany, T. Zhang, X. Lu, F. Ye and B. Liu, *Nano Res.*, 2024, **17**, 2655–2662.
- 11 S. Yi, Z. Su, H. L. Chen, Z. Q. Zhao, X. W. Wang, Y. Y. Zhang, B. Niu and D. H. Long, *Appl. Catal., B*, 2024, **348**, 123853.
- 12 T. Zhu, J. Pan, Z. An, R. Zhe, Q. Ou and H.-E. Wang, *J. Mater. Chem. A*, 2022, **10**, 20375–20385.
- 13 S. Naskar, D. Maity, A. Dixit, M. Freitag, K. Kumari, S. K. Singh and M. Deepa, *J. Mater. Chem. A*, 2024, **12**, 15203–15226.
- 14 T. Zhu, C. Xia, B. Wu, J. Pan, H. Yang, W. Zhang and B. Y. Xia, *Appl. Catal., B*, 2024, **357**, 124315.
- 15 R. Ren, G. Liu, J. Y. Kim, R. E. A. Ardhi, M. X. Tran, W. Yang and J. K. Lee, *Appl. Catal., B*, 2022, **306**, 121096.
- 16 C. Hu, L. Chen, Y. Hu, A. Chen, L. Chen, H. Jiang and C. Li, *Adv. Mater.*, 2021, **33**, 2103558.
- 17 Q. M. Zhang, M. Wei, Q. W. Dong, Q. Z. Gao, X. Cai, S. S. Zhang, T. Yuan, F. Peng, Y. P. Fang and S. Y. Yang, *J. Energy Chem.*, 2023, **79**, 83–91.
- 18 H. T. Xu, W. Y. Yang, M. Li, H. B. Liu, S. Q. Gong, F. Zhao, C. L. Li, J. J. Qi, H. H. Wang, W. C. Peng and J. P. Liu, *Small*, 2024, **20**, 2310972.
- 19 B. D. Boruah, A. Mathieson, B. Wen, S. Feldmann, W. M. Dose and M. De Volder, *Energy Environ. Sci.*, 2020, **13**, 2414–2421.
- 20 B. Deka Boruah, A. Mathieson, S. K. Park, X. Zhang, B. Wen, L. Tan, A. Boies and M. De Volder, *Adv. Energy Mater.*, 2021, **11**, 2100115.
- 21 Y. Liu, Y. Liu, X. Wu and Y. R. Cho, *ACS Sustain. Chem. Eng.*, 2023, **11**, 13298–13305.
- 22 Ü. Ö. A. Arier and B. Ö. Uysal, *Surf. Coat. Technol.*, 2016, **302**, 482–486.
- 23 S. Zafar, M. Sharma, K. M. P. Shai, N. Karmodak, S. K. Singh and B. Lochab, *J. Mater. Chem. A*, 2024, **12**, 32947–32956.
- 24 L. Zhang, Y. Xuan, Q. Wang, Z. Zhu, D. Zhao, X. Liu, Q. Zhu and K. Zhang, *J. Mater. Chem. A*, 2024, **12**, 15361–15372.
- 25 M. Zhang, L. Pan, Z. Jin, X. Wang, H. Mei, L. Cheng and L. Zhang, *Adv. Energy Mater.*, 2023, **13**, 2204058.
- 26 R. T. Chen, Z. F. Ren, Y. Liang, G. H. Zhang, T. Dittrich, R. Z. Liu, Y. Liu, Y. Zhao, S. Pang, H. Y. An, C. W. Ni, P. W. Zhou, K. L. Han, F. T. Fan and C. Li, *Nature*, 2022, **610**, 296–301.
- 27 Y. Lu, H. Andersen, R. Wu, A. M. Ganose, B. Wen, A. Pujari, T. Wang, J. Borowiec, I. P. Parkin, M. De Volder and B. D. Boruah, *Small*, 2024, **20**, 2308869.
- 28 W. W. Zha, Q. S. Ruan, L. Ma, M. Liu, H. W. Lin, L. T. Sun, Z. M. Sun and L. Tao, *Angew. Chem., Int. Ed.*, 2024, **63**, e202400621.
- 29 M. Wilhelm, R. Adam, A. Bhardwaj, I. Neumann, S. H. Cho, Y. Yamada, T. Sekino, J. Tao, Z. Hong, T. Fischer and S. Mathur, *Adv. Eng. Mater.*, 2023, **25**, 2200765.
- 30 X. Y. Wen, Y. T. Zhong, S. Chen, Z. C. Yang, P. Y. Dong, Y. Q. Wang, L. H. Zhang, Z. Wang, Y. Jiang, G. F. Zhou, J. M. Liu and J. W. Gao, *Adv. Sci.*, 2024, **11**, 2309555.
- 31 J. W. Li, Z. Y. Huang, C. Wang, L. Tian, X. Q. Yang, R. F. Zhou, M. N. Ghazzal and Z. Q. Liu, *Appl. Catal., B*, 2024, **340**, 123181.