



Cite this: *Catal. Sci. Technol.*, 2016,  
6, 577

## Ru/TiO<sub>2</sub>-catalysed hydrogenation of xylose: the role of the crystal structure of the support†

Carlos Hernandez-Mejia,<sup>a</sup> Edwin S. Gnanakumar,<sup>a</sup> Alma Olivos-Suarez,<sup>b</sup> Jorge Gascon,<sup>b</sup> Heather F. Greer,<sup>c</sup> Wuzong Zhou,<sup>c</sup> Gadi Rothenberg<sup>a</sup> and N. Raveendran Shiju<sup>\*a</sup>

Effective dispersion of the active species over the support almost always guarantees high catalytic efficiency. To achieve this high dispersion, a favourable interaction of the active species with the support is crucial. We show here that the crystal structure of the titania support determines the interaction and consequently the nature of ruthenium particles deposited on the support. Similar crystal structures of RuO<sub>2</sub> and rutile titania result in a good lattice matching and ensure a better interaction during the heating steps of catalyst synthesis. This helps maintain the initial good dispersion of the active species on the support also in the subsequent reduction step, leading to better activity and selectivity. This highlights the importance of understanding the physico-chemical processes during various catalyst preparation steps, because the final catalyst performance often depends on the type of intermediate structures formed during the preparation.

Received 4th July 2015,  
Accepted 21st August 2015

DOI: 10.1039/c5cy01005e

[www.rsc.org/catalysis](http://www.rsc.org/catalysis)

### 1. Introduction

Lignocellulosic biomass is an excellent feedstock for chemical synthesis. It is renewable, abundantly available and does not compete with food. Consequently, several groups are focused on converting cellulose and hemicellulose into various industrially important chemicals.<sup>1–12</sup> Among these chemicals, sugar alcohols attract particular interest, because of the strong market demand from the food and nutraceuticals sectors. Cellulose and hemicellulose can be hydrolysed using acid catalysis into monomeric sugars, that are then hydrogenated to sugar alcohols.<sup>13–15</sup> Converting cellulose into C<sub>6</sub> sugar alcohols such as sorbitol and mannitol over supported metal catalysts is well studied.<sup>16–21</sup> Conversely, there are few reports on converting hemicellulose into the corresponding C<sub>5</sub> sugar alcohols using solid catalysts.<sup>14,22,23</sup> In this work, we focused on the hydrogenation step from xylose (a hydrolysis product of beechwood hemicellulose) to xylitol, an extensively used compound in the food, cosmetics, and pharmaceutical sectors.<sup>24–26</sup> With an estimated market of \$340m, xylitol is

one of the most popular sweeteners.<sup>27</sup> Moreover, its relative inertness gives it a long shelf life, an important feature for pharmaceutical preparations.<sup>28,29</sup> Currently, xylitol is made *via* catalytic hydrogenation over RANEY® nickel.<sup>30</sup> Although this catalyst is cheap, it deactivates quickly due to leaching and/or poisoning.<sup>31,32</sup> Any leached Ni must be removed, leading to additional costs.<sup>27</sup> Alternatively, one can use noble metals such as Ru, Rh and Pd.<sup>33–37</sup> Ru is the most effective, but it is much more expensive than Ni, thus its efficiency and long-term stability must be high to be a viable alternative.

For heterogeneous catalysts, the active species such as the metal is often supported on a high surface area metal oxide. The interaction between metals and oxide supports, so-called metal-support interactions, then becomes important.<sup>38</sup> Tauster *et al.* proposed the concept of strong metal-support interaction (SMSI) in 1978 to describe the drastic changes in the chemisorption properties of Group 8–10 noble metals supported on TiO<sub>2</sub>.<sup>39</sup> Later, SMSI was widely observed in many metal/oxide catalytic systems. Electronic or geometric factors may be responsible for SMSI. The Electronic factors involve charge transfer between the metal and the oxide. As a result, the electronic structure of the metal will be perturbed.


Here we report the catalytic hydrogenation of xylose to xylitol (eqn (1)) using Ru supported on TiO<sub>2</sub>. We show that the deposition of Ru on TiO<sub>2</sub> gives highly efficient catalyst. However, we also show that the efficiency depends significantly on the crystal structure of the support. The key lies in the catalyst preparation steps, wherein the crystal structures

<sup>a</sup> Van't Hoff Institute for Molecular Sciences, University of Amsterdam, P.O. Box 94157, 1090GD Amsterdam, The Netherlands. E-mail: [n.r.shiju@uva.nl](mailto:n.r.shiju@uva.nl);  
Web: <http://hims.uva.nl/hcsc>

<sup>b</sup> Delft University of Technology, Catalysis Engineering Section, Julianalaan 136, 2628 BL Delft, The Netherlands

<sup>c</sup> School of Chemistry, University of St Andrews, St Andrews KY16 9ST, UK

† Electronic supplementary information (ESI) available: XRD, SEM and EDX analysis, characterization of spent samples, detailed product distribution. See DOI: 10.1039/c5cy01005e

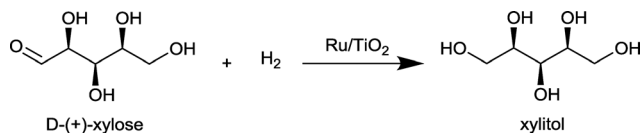

(1)

in a stainless steel autoclave at 120–160 °C under 20 bar hydrogen. After the desired reaction time, the autoclave was quenched in an ice bath and the products were analysed using HPLC.

Examining the substrate conversion and product yield at 120 °C, one sees immediately a striking performance difference between the anatase and rutile supports (Fig. 1). Anatase supported Ru (A) gave a mixture of products, with low xylitol selectivity. Interestingly, Ru supported on rutile titania (catalyst C) gave 100% xylose conversion and up to 98% yield for xylitol in 15 min. Catalyst D showed similar behaviour to C, indicating that the Ru properties are influenced by the rutile part of the support. B was more active and selective than A, though still worse than rutile supported Ru. Note that B is still predominantly anatase, but has a lower surface area compared to A. Thus, the surface area seems not to be critical here. The same trends in performance were observed at 140 °C and 160 °C, albeit that increasing temperature decreased the xylitol yield (see Fig. 1), giving instead more of the diastereomers arabitol and adonitol (Fig. 2).

The kinetic studies at 120 °C (Fig. 3) confirm that C and D are more active and selective than the anatase based catalysts A and B. Xylitol was selectively formed (98%) within 15 minutes over C and D. The selectivity decreased marginally with increasing the reaction time. A does not show a major xylitol yield at any given time. For B, a maximum xylitol yield is observed at 180 min. Full conversion was not achieved with both A and B under these conditions.

A recycling test for C and D was carried out at 120 °C. The reaction mixture after each time was centrifuged and the liquid phase was separated from the catalyst. This liquid phase was analysed and the catalyst was washed with distilled water. Conversions and xylitol yields were constant even after the fourth recycling test, showing the stability of these two catalysts.

In order to explain the activity trends, we characterized the catalysts by several techniques. The XRD patterns (see ESI†) confirmed that A and C are predominantly anatase and rutile respectively. We also calculated the percentage of rutile phase in each catalyst (B, C and D have 1.1%, 99.5% and



Fig. 2 Diastereomers of xylitol.

34.5% rutile phase, respectively). Note that the most predominant crystallographic plane for anatase is (101) and for rutile is (110).<sup>40</sup> These planes were used for calculating the ratio of the phases and for the images shown in Fig. 6. Diffraction peaks corresponding to ruthenium species could not be observed, indicating high dispersion of supported ruthenium. H<sub>2</sub> TPR profiles of the calcined catalysts (Fig. 4) show a sharp peak between 180 and 230 °C, which can be assigned to the reduction of RuO<sub>2</sub>.<sup>36,41,42</sup> Hydrogen intake from the catalysts A, B, C and D are 1254, 1438, 739 and 507 μg mol<sup>-1</sup> respectively. Anatase-based catalysts have a higher hydrogen consumption compared to rutile catalysts. The second peak on the TPR profile (between 270 and 450 °C) may be ascribed to a partial reduction of the support, inducing the formation of oxygen vacancies or Ti<sup>3+</sup> species.<sup>43</sup>

SEM analysis (ESI†) revealed a uniform dispersion of ruthenium over C after calcination as well as after reduction. In contrast, EDX detected visible metallic agglomerations on the surface of A and B, before and after reduction. We further studied the catalysts by TEM, which provided important information (Fig. 5). The rutile TiO<sub>2</sub> particles (Fig. 5b) were of several hundred nanometers in diameter. In contrast, the anatase TiO<sub>2</sub> particles (Fig. 5a) were smaller in size. Since the rutile form was obtained by high temperature calcination, formation of the larger titania particles is expected. Importantly, a homogeneous surface covering of Ru particles was observed on rutile surface (C). The typical Ru particle size is between 5–7 nm (see also ESI†). On the contrary, Ru particles were very localised on the anatase surface. These are much bigger (see the dark particle in Fig. 5a) and could easily be detected by EDX (SEM images in ESI†).

The uniform distribution of Ru nanoparticles with a narrow size distribution over rutile titania (catalysts C and D) suggests a lattice anchoring interaction between Ru and the



Fig. 1 Xylitol yield at different temperatures after 3 h reaction. Reaction conditions: 20 bar H<sub>2</sub>, xylose : Ru ratio 100 : 1 (w/w), solvent water.



Fig. 3 Xylitol yield during different reaction times at 120 °C.





Fig. 4 TPR profiles for calcined Ru/TiO<sub>2</sub> catalysts.



Fig. 5 The TEM images of catalysts A (a) and C (b) show the agglomeration of the Ru on the anatase support and the fine dispersion on the rutile support.

support. Since RuO<sub>2</sub> also has a rutile-type structure, we expect a high degree of lattice matching between RuO<sub>2</sub> and the rutile titania support, preventing the agglomeration of Ru particles during the calcination step (Fig. 6, left).<sup>44–46</sup> Since there is no such matching with the anatase support, the RuO<sub>2</sub> particles are less stable (Fig. 6, right). Thus, the agglomeration of Ru on anatase, as shown by TEM, can explain the lower catalytic performance compared with rutile catalysts. RuO<sub>2</sub> nanoparticles are reported to be easily



Fig. 6 Atomic structures of RuO<sub>2</sub> on rutile (left) and anatase (right) TiO<sub>2</sub> showing the high degree of lattice matching of RuO<sub>2</sub> on rutile TiO<sub>2</sub> (created by viewerlite software).<sup>50</sup>

aggregated in oxidative atmosphere due to the volatility of oxidized ruthenium.<sup>47</sup> This is the case observed in the RuO<sub>2</sub>/anatase-TiO<sub>2</sub>. However, the intimate interaction between RuO<sub>2</sub> and rutile-TiO<sub>2</sub>, as a result of their high degree of lattice matching stabilizes the RuO<sub>2</sub> and maintains its high dispersion during calcination and further reduction. The binding nature of RuO<sub>2</sub> nanoclusters on rutile TiO<sub>2</sub> (110) and anatase TiO<sub>2</sub> (101) surfaces was studied by first-principle calculations previously.<sup>48</sup> These studies showed that the adsorption energy of RuO<sub>2</sub> cluster on rutile is larger than that on anatase due to more interfacial bonds formed between cluster and surface. This further confirms our experimental observations that the rutile support provides highly dispersed Ru with uniform nanosize, leading to high activity and stability in xylose hydrogenation to xylitol. When the support contains both rutile and anatase (D), the Ru is predominantly present on the rutile. We observed such behaviour previously for vanadia supported on Al<sub>2</sub>O<sub>3</sub>-MgO. Vanadium species was preferentially attached to Al<sub>2</sub>O<sub>3</sub> at low loadings and to MgO at high loading.<sup>49</sup>

We also analysed the catalysts after the reaction by XRD and TEM. The peak at  $2\theta = 25^\circ$  was slightly broader for the spent A catalyst. There was no other major change in the XRD patterns before and after the reaction for any of the catalysts (Fig. S2†). TEM images did not show any obvious changes for the spent catalysts (see ESI†). The Ru particles are small and highly dispersed for the spent catalyst C as in the fresh catalysts. This indicates that the structure remains unchanged during the reaction. Indeed, this catalyst retained the same level of activity after multiple recycling tests.

Based on the information from electron microscopy and TPR, we can also infer that large Ru species on anatase TiO<sub>2</sub> leads to a higher reducibility of the support. As mentioned before, the peak between 270 and 450 °C in the TPR of anatase-based catalysts may be ascribed to a partial reduction





Fig. 7  $\text{Ti}^{3+}$  acting as a Lewis base for xylose retro-aldol reaction to glycols.

of the support, inducing the formation of oxygen vacancies and  $\text{Ti}^{3+}$  species.<sup>43</sup> This could happen most likely at the interface between the Ru species and  $\text{TiO}_2$  support. These species have two main effects. First they alter the charge transfer between the metal and its support leading to changes on the catalyst's performance.<sup>51,52</sup> Second, the presence of  $\text{Ti}^{3+}$  species interacting with the C–O bond has been related in previous studies<sup>34,53</sup> with either a hydrogenolysis pathway where this C–O bond is cleaved or as a Lewis base leading to a retro-aldol reaction (Fig. 7). Thus, the production of glycols by anatase based catalysts can be explained. Moreover, the surface is deficient in oxygen, leading to aldehyde decomposition in favour of oxygen restoration at the lattice, forming different by-products.<sup>54,55</sup> All these effects collectively lead to a lower selectivity for the anatase-supported Ru catalysts.

## Conclusions

$\text{Ru}/\text{TiO}_2$  is an effective catalyst for xylose hydrogenation to xylitol. However, care should be taken in preparing the catalyst, as the crystal structure of  $\text{TiO}_2$  support has a strong influence on the efficiency of the final catalyst. Thus, ruthenium supported on rutile titania gives high conversion as well as high selectivity to xylitol, in spite of a low surface area, while Ru on anatase is less active and non-selective. TEM analysis revealed well dispersed Ru particles, 5–7 nm size over the rutile-titania whereas bigger Ru agglomerations were found on anatase  $\text{TiO}_2$ . This can be explained by a high degree of lattice matching for rutile since  $\text{RuO}_2$  also has a rutile-type structure, preventing mobility of Ru particles during heating treatments. Small dispersed Ru particles mean more active centres for hydrogenation, improved charge transfer with the support and easier reduction of any superficially oxidised ruthenium. Additionally, possible formation of  $\text{Ti}^{3+}$  species over anatase based catalysts may serve as Lewis base sites modifying the reaction pathway thus lowering the selectivity further. This work shows the importance of understanding the intermediate steps in the catalyst synthesis process.

## Acknowledgements

CHM thanks the National Council of Science and Technology, Mexico (Consejo Nacional de Ciencia y Tecnología CONACyT) for financial support (Scholarship 216968). WZ and HFG thank the EPSRC for a Platform grant (EP/K015540/1). This

work is part of the Research Priority Area Sustainable Chemistry of the UvA, <http://suschem.uva.nl>.

## Notes and references

- W. Keim, *Pet. Chem.*, 2010, **50**, 298–304.
- T. Werpy and G. Petersen, *Top value added chemicals from biomass, volume I: results of screening for potential candidates from sugars and synthesis gas*, Pacific Northwest National Laboratory, 2004.
- B. Kamm, P. R. Gruber and M. Kamm, *Biorefineries – Industrial Processes and Products*, Wiley-VCH, Weinheim, 2006.
- R. Beerthuis, M. Granollers, D. R. Brown, H. J. Salavagione, G. Rothenberg and N. R. Shiju, *RSC Adv.*, 2015, **5**, 4103–4108.
- Z. Strassberger, F. van der Klis, D. S. van Es, S. Tanase, P. Prinsen and G. Rothenberg, *Green Chem.*, 2015, **17**, 325–334.
- E. V. Ramos-Fernandez, N. J. Geels, N. R. Shiju and G. Rothenberg, *Green Chem.*, 2014, **16**, 3358–3363.
- P. Demma Carà, R. Ciriminna, N. R. Shiju, G. Rothenberg and M. Pagliaro, *ChemSusChem*, 2014, **7**, 835–840.
- V. Subbiah, P. van Zwol, A. C. Dimian, V. Gitis and G. Rothenberg, *Top. Catal.*, 2014, **57**, 1545–1549.
- A. Corma and P. Serna, *Science*, 2006, **332**, 313.
- M. Dusselier, M. Mascal and B. F. Sels, *Top. Curr. Chem.*, 2014, **353**, 1–40.
- I. Delidovich, K. Leonhard and R. Palkovits, *Energy Environ. Sci.*, 2014, **7**, 2803–2830.
- C. Caro, K. Thirunavukkarasu, M. Anilkumar, N. R. Shiju and G. Rothenberg, *Adv. Synth. Catal.*, 2012, **354**, 1327–1336.
- P. Maki-Arvela, T. Salmi, B. Holmbom, S. Willfor and D. Y. Murzin, *Chem. Rev.*, 2011, **111**, 5638–5666.
- P. Demma Carà, M. Pagliaro, A. Elmekawy, D. R. Brown, P. Verschuren, N. R. Shiju and G. Rothenberg, *Catal. Sci. Technol.*, 2013, **3**, 2057–2061.
- W. Y. Lim and J. Dumesic, *Angew. Chem., Int. Ed.*, 2013, **52**, 1270–1274.
- P. L. Dhepe and A. Fukuoka, *Catal. Surv. Asia*, 2007, **11**, 186.
- M. Yabushita, H. Kobayashi and A. Fukuoka, *Appl. Catal., B*, 2014, **145**, 1–9.
- Y.-B. Huang and Y. Fu, *Green Chem.*, 2013, **15**, 1095–1111.
- A. M. Ruppert, K. Weinberg and R. Palkovits, *Angew. Chem., Int. Ed.*, 2012, **51**, 2564–2601.
- R. Palkovits, K. Tajvidi, J. Procelewska, R. Rinaldi and A. Ruppert, *Green Chem.*, 2010, **12**, 972–978.
- A. Fukuoka and P. L. Dhepe, *Angew. Chem., Int. Ed.*, 2006, **45**, 5161–5163.
- F. Cherubini and A. H. Strømman, *Biofuels, Bioprod. Biorefin.*, 2011, **5**, 548–561.
- S. Dutta, *RSC Adv.*, 2012, **2**, 12575–12593.
- C. Hayes, *J. Dent. Educ.*, 2001, **65**, 1106–1109.
- K. Mäkinen, *J. Appl. Nutr.*, 1992, **44**, 16–28.
- M. Uhari, T. Kontiokari, M. Koskela and M. Niemelä, *Br. Med. J.*, 1996, **313**, 1180–1184.
- M. Yadav, D. K. Mishra and J. S. Hwang, *Appl. Catal., A*, 2012, **425–426**, 110–116.



- 28 S. S. Schiffman and C. A. Gatlin, *Neurosci. Biobehav. Rev.*, 1993, **17**, 313–345.
- 29 H. Förster, H. L. Sipple and K. W. McNutt, *Sugars in Nutrition*, Academic Press, New York, 1974.
- 30 A. Melaja, L. Hämäläinen and H. O. Heikkilä, *Finland Pat.*, FI 589388, 1981.
- 31 J. P. Mikkola and T. Salmi, *Chem. Eng. Sci.*, 1999, **54**, 1583–1588.
- 32 J. P. Mikkola and T. Salmi, *Catal. Today*, 2001, **64**, 271–277.
- 33 J. Wisniak, M. Hershkowitz and S. Stein, *Ind. Eng. Chem. Prod. Res. Dev.*, 1974, **13**, 232–236.
- 34 C. Newman, X. Zhou, B. Goundie, I. T. Ghampson, R. A. Pollock, Z. Ross, M. C. Wheeler, R. W. Meulenberg, R. N. Austin and B. G. Frederick, *Appl. Catal., A*, 2014, **477**, 64–74.
- 35 M. Besson, P. Gallezot, A. Pigamo and S. Reifsnyder, *Appl. Catal., A*, 2003, **250**, 117–124.
- 36 J. W. da-Silva and A. J. G. Cobo, *Appl. Catal., A*, 2003, **252**, 9–16.
- 37 S. J. Tauster, S. C. Fung and R. L. Garten, *J. Am. Chem. Soc.*, 1978, **100**, 170–175.
- 38 N. R. Shiju, *ChemCatChem*, 2011, **3**, 112–114.
- 39 S. J. Tauster, *Acc. Chem. Res.*, 1987, **20**.
- 40 K. Sivarajani and C. S. Gopinath, *J. Mater. Chem.*, 2011, **21**, 2639–2647.
- 41 T. Omotoso, S. Boonyasuwat and S. P. Crossley, *Green Chem.*, 2013, **16**, 645–652.
- 42 B. D. McNicol and R. T. Short, *J. Electroanal. Chem.*, 1978, **92**, 115–120.
- 43 T. Ekou, L. Ekou, A. Vicente, G. Lafaye, S. Pronier, C. Especel and P. Marecot, *J. Mol. Catal. A: Chem.*, 2011, **337**, 82–88.
- 44 J. M. G. Carballo, E. Finocchio, S. Garcia, S. Rojas, M. Ojeda, G. Busca and J. L. G. Fierro, *Catal. Sci. Technol.*, 2011, **1**, 1013–1023.
- 45 J. Li, G. Lu, G. Wu, D. Mao, Y. Guo, Y. Wang and Y. Guo, *Catal. Sci. Technol.*, 2014, **4**, 1268–1275.
- 46 G. A. Rizzi, A. Magrin and G. Granozzi, *Phys. Chem. Chem. Phys.*, 1999, **1**, 709–711.
- 47 Y. Zhang, X. Wang, Y. Zhu and T. Zhang, *Appl. Catal., B*, 2013, **129**, 382–393.
- 48 H. Dong, L. Zhang and X. Zhou, *Theor. Chem. Acc.*, 2014, **133**, 1–9.
- 49 Z. Strassberger, E. V. Ramos-Fernandez, A. Boonstra, R. Jorna, S. Tanase and G. Rothenberg, *Dalton Trans.*, 2013, **42**, 5546–5553.
- 50 G. W. Watson, E. T. Kelsey, N. H. de Leeuw, D. J. Harris and S. C. Parker, *J. Chem. Soc., Faraday Trans.*, 1996, **92**, 433.
- 51 Z. Jiang, W. Zhang, L. Jin, X. Yang, F. Xu, J. Zhu and W. Huang, *J. Phys. Chem.*, 2007, **111**, 12434–12439.
- 52 S. Fischer, F. Schneiderb and K.-D. Schierbaum, *Vacuum*, 1996, **47**, 1149–1152.
- 53 K. Kreuzer and R. Kramer, *J. Catal.*, 1997, **167**, 391–399.
- 54 H. Idriss, K. S. Kim and M. A. Barteau, *Surf. Sci.*, 1992, **262**, 113–127.
- 55 G. Lu, A. Linsebigler and J. T. Yates, *J. Phys. Chem.*, 1995, **99**, 7626–7631.

