Chemical Science



EDGE ARTICLE

View Article Online
View Journal | View Issue



Cite this: Chem. Sci., 2021, 12, 13316

dll publication charges for this article have been paid for by the Royal Society of Chemistry

Received 6th July 2021 Accepted 15th September 2021

DOI: 10.1039/d1sc03680g

rsc.li/chemical-science

A pillar[5]arene-based covalent organic framework with pre-encoded selective host-guest recognition†

Lu Liu,^{ac} Yiming Hu, [©] Shaofeng Huang, [©] Yinghua Jin, [©] Jingnan Cui, [©] Weitao Gong [©] *^{ab} and Wei Zhang [©] *^c

It is highly desirable to maintain both permanent accessible pores and selective molecular recognition capability of macrocyclic cavitands in the solid state. Integration of well-defined discrete macrocyclic hosts into ordered porous polymeric frameworks (e.g., covalent organic frameworks, COFs) represents a promising strategy to transform many supramolecular chemistry concepts and principles well established in the solution phase into the solid state, which can enable a broad range of practical applications, such as high-efficiency molecular separation, heterogeneous catalysis, and pollution remediation. However, it is still a challenging task to construct macrocycle-embedded COFs. In this work, a novel pillar[5]arene-derived (P5) hetero-porous COF, denoted as P5-COF, was rationally designed and synthesized. Featuring the unique backbone structure, P5-COF exhibited selective adsorption of C_2H_2 over C_2H_4 and C_2H_6 , as well as significantly enhanced host–guest binding interaction with paraquat, in comparison with the pillar[5]arene-free COF analog, Model-COF. The present work established a new strategy for developing COFs with customizable molecular recognition/separation properties through the bottom-up "pre-porous macrocycle to porous framework" design.

Introduction

Covalent organic frameworks (COFs) represent a class of crystalline porous materials constructed with diverse organic building blocks *via* covalent bonds.¹⁻⁵ Featuring high surface area, large pore volume, high chemical/thermal stability, and tunable pore topologies, COFs have become a promising platform for gas adsorption and separation,⁶⁻¹⁰ comparable to conventional porous materials, such as zeolites and metalorganic frameworks (MOFs).¹¹⁻¹³ However, specific supramolecular host–guest interactions, which have been commonly employed in the solution phase to realize selective molecular binding, have rarely been explored in the COF system.^{14,15} One possible way to address this issue is to incorporate macrocyclic cavitands into COFs. Such a "pre-porous macrocycle to porous framework" design would combine the merits of both macrocyclic hosts, with inherent porosity and selective molecular

recognition properties, and COFs with stable backbones and a large pore distribution for mass transfer.¹⁶⁻²⁰

Pillar[n]arenes,21-23 a class of macrocyclic cavitands with intrinsic confined pores and selective guest binding capability, are attractive candidates for integration into COFs as host molecules.24-26 Although interesting molecular recognition properties of pillar[n] arenes in the solution phase have been demonstrated, they generally exhibit poor guest binding capability in the solid state due to their random packing.27-32 The opening channels are largely blocked, and the intrinsic cavities are buried inside the solid matrix and not accessible to the guest species.33,34 Meanwhile, the supramolecular structures assembled via noncovalent interactions are vulnerable and tend to collapse upon guest removal. 35,36 Therefore, it is challenging to maintain the permanent porosity and selective guest binding properties of pillar[n] arenes in the solid state. It is envisioned that the integration of pillar [n] arene macrocycles into COFs can overcome the above-mentioned drawbacks. To date, although amorphous porous organic polymers with pillar[n]arenes incorporated have been conceived and triggered some interesting applications, 37-44 to the best of our knowledge, the pillar [n] are ne-based crystalline COFs have not been realized, likely due to the synthetic challenges.

Herein, we report the rational design and synthesis of a new COF, denoted as **P5-COF**, derived from pre-porous pillar[5] arene-based diamine (**APP5**) and 1,3,5-triformylbenzene (**TFB**) *via* one-pot imine condensation. To demonstrate the critical

[&]quot;State Key Laboratory of Fine Chemicals, School of Chemical Engineering, Dalian University of Technology, Dalian 116024, P. R. China. E-mail: wtgong@dlut.edu.cn bEngineering Laboratory of Boric and Magnesic Functional Material Preparative and Applied Technology, Dalian, Liaoning Province, 116024, P. R. China

Department of Chemistry, University of Colorado Boulder, Boulder, Colorado 80309, USA. E-mail: wei.zhang@colorado.edu

[†] Electronic supplementary information (ESI) available: ¹H NMR, ¹³C NMR, and IR spectra, solid-state NMR spectrum, SEM images, TGA curve, PXRD patterns and nitrogen adsorption isotherms. See DOI: 10.1039/d1sc03680g

Edge Article Chemical Science

role of pillar[5]arene macrocycles for the observed selective molecular recognition in the resulting **P5-COF**, a model COF without pillar[5]arene moieties, named **Model-COF** was also prepared. The experiments clearly showed that **P5-COF** exhibits superior performance in selective C_2H_2 gas adsorption over C_2H_4 and C_2H_6 , as well as significantly enhanced host–guest binding interaction with paraquat in comparison with **Model-COF**, likely owing to the presence of pillar[5]arene moieties.


Results and discussion

We synthesized **P5-COF** and **Model-COF** through imine condensation between 1,3,5-triformylbenzene (**TFB**) and **APP5** or 4,4'-diamino-*p*-terphenyl (**TP**) in mixed solvents of dioxane, mesitylene and acetic acid aqueous solution at 120 °C for 3 days, respectively (Scheme 1). **P5-COF** and **Model-COF** were characterized by FT-IR spectroscopy, ¹³C CP-MAS NMR spectroscopy, TGA, SEM and PXRD analysis. The FT-IR spectra of both **P5-COF** and **Model-COF** show the disappearance of the aldehyde peak at 1693 cm⁻¹ and amine peaks at 3449 and 3356 cm⁻¹. Meanwhile, the appearance of the −C≔N stretching peak at 1624 cm⁻¹ supports the formation of imine bonds *via* the condensation of aldehyde and primary amine (Fig. S3 and S4†).

The cross-polarization magic-angle spinning (CP-MAS) NMR spectrum of P5-COF shows a peak around 157 ppm, corresponding to the carbon atom of the -C=N bond, and signals at 122-138 ppm, which can be assigned to the carbon atoms of the phenyl groups (Fig. S5 and S6†). The peaks with the chemical shifts around 55 and 37 ppm were assigned to the methoxy carbon and benzyl carbon in pillar[5]arenes, respectively (Fig. S5†). Thus, the solid-state NMR data support the structure of P5-COF. The thermogravimetric analysis (TGA) of the materials showed good thermal stability with a decomposition temperature of 420 °C for Model-COF and 400 °C for P5-COF (Fig. S7†). Furthermore, the morphologies of the two COFs were characterized by SEM and TEM (Fig. S8 and S9†). P5-COF shows irregular particles with rather smooth surfaces, whereas Model-COF shows a moss-like surface morphology. The good crystallinity of P5-COF was confirmed by powder X-ray diffraction (PXRD) (Fig. 1a). To determine the packing structure of P5-COF, the eclipsed and staggered stacking conformations of the pillar [5]arene structure were simulated. In order to construct the

most energy stable packing pattern, we examined the single crystal packing mode of pillar[5]arene small molecules. We found that CH- π interactions between pillar[5]arene molecules largely stabilize the crystal structure.45 Thus, we introduced similar CH- π interactions when incorporating the pillar[5] arene moieties along the z axis to minimize the system energy. Accordingly, we built a P5-COF structure in the P3 space group with Pawley-refined unit cell parameters a = 37.2308 Å, b =35.9837 Å, c = 13.3034 Å, $\alpha = 86.93^{\circ}$, $\beta = 89.76^{\circ}$, and $\gamma = 116.91^{\circ}$ (Fig. 1c and d). The PXRD patterns of P5-COF exhibit three intense peaks at 2.88°, 5.04° and 7.77°, which correspond to the (100), (110) and (210) reflections, respectively. The Pawleyrefined PXRD patterns agree well with the experimental results with R_p and R_{wp} values of 1.84% and 2.26%, respectively (Fig. 1a). The as-obtained Model-COF also exhibits good crystallinity, showing a strong and sharp peak at 2.42° in the PXRD spectrum, which could be assigned to the (100) Bragg degree reflection. The peaks at 4.69° and 5.36° were assigned to the (110) and (200) reflections, respectively (Fig. S10†). To explore the stability of these frameworks, P5-COF and Model-COF were immersed in different organic solvents and aqueous solutions (EtOH, THF, DMF, water, aqueous HCl (2 M), and NaOH (2 M)) for 24 hours. The PXRD data obtained before and after treatment barely showed any difference, which indicates high chemical stability of both COFs (Fig. S11†).

Nitrogen sorption isotherms at 77 K were then measured to evaluate the porosity of the COFs. Both the isotherms of P5-COF and Model-COF present type-IV adsorption. The BET surface areas of P5-COF and Model-COF are calculated to be 381 $\text{m}^2\,\text{g}^{-1}$ and 134 m² g⁻¹, respectively (Fig. 1b and S12 \dagger). The pore size distributions (PSDs) were evaluated with the quenched solid density functional theory (QSDFT) equilibrium model. Model-COF exhibits a pore size distribution in the range of 2.0–3.2 nm, which is in good agreement with the literature report (Fig. S14†).46 P5-COF exhibits two major pores with the sizes of 0.78 nm and 1.43 nm, which likely result from the intrinsic pillarene macrocycles and internal aligned channels in the COF. It is worth noting that the pore diameter of 0.78 nm is in agreement with the cavity size of pillar[5] arenes, which supports the presence of the permanent pillar[5] cavity in the COF. 47 The calculated total pore volumes of Model-COF and P5-COF are 0.53 and 0.32 cm 3 g $^{-1}$, respectively (Table S1 \dagger).

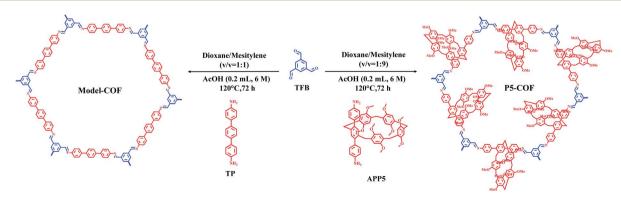

Scheme 1 Synthetic routes to P5-COF and Model-COF.

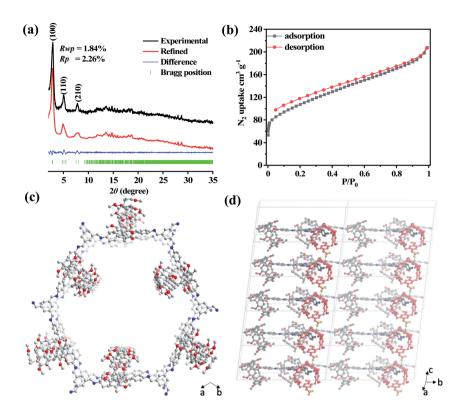


Fig. 1 (a) Experimental and simulated PXRD patterns of P5-COF; (b) N_2 adsorption isotherms of P5-COF at 77 K; (c and d) top view (c) and side view (d) of P5-COF in the AA stacking model. The green dash indicates the CH- π stabilizing interactions.

The unique pillar-shaped architectures and rigid π -rich cavities of pillar[n]arenes make them high affinity hosts for paraquat and other electron-deficient molecules. However, conventionally such guest-binding behavior has been mostly observed in the homogeneous solution. He solid state, due to random molecular aggregation, many intrinsic pores are blocked, thus dramatically decreasing the guest-binding capacity. By integrating pillar[5] arenes into ordered COFs, we envisioned that such long-standing problems in their guest binding in a heterogeneous environment can be overcome.

To explore the binding behavior of the **P5-COF** solid material toward paraquat in a heterogeneous environment, the absorption isotherm experiments with various concentrations of

paraquat (0–0.2 mM) at room temperature were conducted. As shown in Fig. 2a, the Langmuir equilibrium isotherm model of paraquat matches very well with a good distribution coefficient. We found that **P5-COF** exhibits a good adsorption capacity for paraquat ($q_{\rm max}=31~{\rm mg~g^{-1}}$). Furthermore, as shown in Fig. S16,† the adsorption efficiency remained >80% even after five cycles of the adsorption study, and **P5-COF** retained its chemical structure and crystallinity after five cycles based on PXRD and FT-IR spectra. By contrast, **Model-COF** did not show any obvious adsorption of paraquat, which is consistent with our assumption that the adsorbed paraquat by **P5-COF** was due to the host–guest interaction between the pillar[5]arene units of **P5-COF** and paraquat. These results support that when a well-

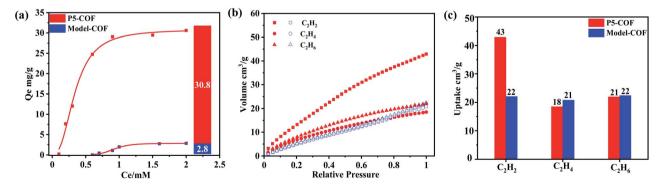


Fig. 2 (a) Langmuir adsorption isotherms of paraquat by P5-COF and Model-COF. Inset: the comparison of the paraquat adsorption capacity of P5-COF and Model-COF; (b) gas adsorption isotherms of P5-COF (red) and Model-COF (blue) at 273 K; (c) comparison of gas adsorption uptakes of P5-COF and Model-COF at 273 K.

Edge Article Chemical Science

defined molecular porous structure is introduced into an ordered porous polymer, the host–guest binding behavior (*e.g.*, binding selectivity, affinity, *etc.*) could be transferred into the polymer matrix; hence, **P5-COF** bridged the gap between the organic porous polymers and the supramolecular macrocycles as pre-porous building blocks.

Given the encouraging results of the paraquat adsorption study, we next explored the gas adsorption properties of P5-COF. Hydrocarbons play a significant role in the petrochemical industry and have been considered as important energy sources due to the high value of these hydrocarbons as chemical feedstock and their wide applications. In this study, C₂H₂, C₂H₄, and C₂H₆ were chosen as the probe molecules to examine the gas adsorption properties. All measurements were conducted at 1 bar and 273 K. The uptakes of C₂H₆, C₂H₄, and C₂H₂ by Model-COF were 22, 21, and 22 cm³ g⁻¹, respectively. At the same temperature and pressure, the uptakes of C₂H₆, C₂H₄, and C₂H₂ by **P5-COF** were 21, 18, and 43 cm³ g⁻¹, respectively. It should be noted that the uptake of C₂H₂ by **P5-COF**was increased by 110%, while the uptake of C₂H₆ and C₂H₄ was decreased slightly when compared to the amount adsorbed by Model-COF (Fig. 2c). This difference in acetylene uptake is presumably due to the more favorable interaction between pillar[5]arene moieties and acetylene molecules through hydrogen bonding and π - π , or C-H-O interactions,54-57 thus showing the potential of P5-COF in selective separation of acetylene. We also calculated the natural selectivity of C₂H₂ over C₂H₄, which is an important parameter in the industrial process of ethylene purification. P5-COF showed a natural selectivity of 2.4, which is comparable to that of many other organic frameworks. 58-60 The selectivity calculated by the ideal adsorption solution theory (IAST) method is 3.2 with a 50: 50 feeding mixture at a total pressure of 1 bar and 273 K. However, as shown in Table S2,† the IAST selectivity of C₂H₂/C₂H₄ is comparable to that of the well-known MOFs such as series ZJNU-14 (2.05), HUST-5 (1.8), and HUST-6 (1.42). In sharp contrast, the Model-COF showed nearly no selectivity for C₂H₂ over C₂H₄ at 273 K. Considering that these two COFs have a similar C₂H₄ uptake amount, the higher C₂H₂ uptake of P5-**COF** mainly results from the interaction between the adsorbent and adsorbate.

Conclusions

In summary, we have synthesized, for the first time, a pillar[5] arene-based COF (P5-COF), which showed heteroporosity and notable C_2H_2 and paraquat adsorption capabilities. More importantly, P5-COF exhibits superior performance in selective C_2H_2 gas adsorption over C_2H_4 and C_2H_6 , as well as significantly enhanced adsorption of paraquat compared with that of pillar [5]arene-free Model-COF. We believe that the macrocyclic structural features of pillar[5]arenes, the connectivity of their intrinsic cavities, and pore size of the framework play a critical role in the performance characteristics of P5-COF. Our study opens new possibilities for developing novel COF materials with specific guest binding capability by integrating host moieties into porous frameworks and harnessing their supramolecular

host-guest binding interactions in the solid state, which conventionally has been possible only in the solution phase.

Data availability

All the data have been included in the ESI.†

Author contributions

Conceptualization and supervision: W. Gong and W. Zhang; synthesis and characterization (XRD, PXRD, TGA, IR, adsorption): L. Liu, Y. Hu, and S. Huang; writing, reviewing, & editing: L. Liu, S. Huang, Y. Hu, Y. Jin, W. Gong and W. Zhang. The ideal adsorption solution theory (IAST) method calculations: S. Huang, all authors proof-read, provided comments, and approved the final version of this manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We are grateful for financial support from the Natural Science Foundation of Liaoning Province [No. 2019-MS-046], the Open Funds of the State Key Laboratory of Rare Earth Resource Utilization (No. RERU2020004) and the Open Sharing Fund for the Large-scale Instruments and Equipments of Dalian University of Technology (No. DUTKFJJ2021086, DUTKFJJ2021122). W. Z. thanks the University of Colorado Boulder. L. L. acknowledges the support of the scholarship from the China Scholarship Council (CSC) under the Grant CSC No. 201906060129.

Notes and references

- A. P. Cote, A. I. Benin, N. W. Ockwig, M. O'Keeffe,
 A. J. Matzger and O. M. Yaghi, *Science*, 2005, 310, 1166–1170.
- 2 S. Y. Ding and W. Wang, Chem. Soc. Rev., 2013, 42, 548-568.
- 3 K. Geng, T. He, R. Liu, S. Dalapati, K.-T. Tan, Z. Li, S. Tao, Y. Gong, Q. Jiang and D. Jiang, *Chem. Rev.*, 2020, **120**, 8814–8933.
- 4 S. Wang, Q. Sun, W. Chen, Y. Tang, B. Aguila, Y. Pan, A. Zheng, Z. Yang, L. Wojtas, S. Ma and F.-S. Xiao, *Matter*, 2020, 2, 416–427.
- 5 Y. Jin, Y. Hu, M. Ortiz, S. Huang, Y. Ge and W. Zhang, *Chem. Soc. Rev.*, 2020, **49**, 4637–4666.
- 6 Y. Zeng, R. Zou and Y. Zhao, Adv. Mater., 2016, 28, 2855–2873.
- 7 T. Banerjee, K. Gottschling, G. Savasci, C. Ochsenfeld and B. V. Lotsch, *ACS Energy Lett.*, 2018, 3, 400–409.
- 8 P. Wang, Q. Xu, Z. Li, W. Jiang, Q. Jiang and D. Jiang, *Adv. Mater.*, 2018, **30**, 1801991–1801998.
- 9 X. Li and K. P. Loh, ACS Mater. Lett., 2019, 1, 327-335.
- 10 S. Huang, Y. Hu, L. L. Tan, S. Wan, S. Yazdi, Y. Jin and W. Zhang, ACS Appl. Mater. Interfaces, 2020, 12, 51517– 51522.

11 P. Yang, W. Zhao, A. Shkurenko, Y. Belmabkhout, M. Eddaoudi, X. Dong, H. N. Alshareef and N. M. Khashab, J. Am. Chem. Soc., 2019, 141, 1847–1851.

Chemical Science

- 12 Y. Zhang, J. Li, X. Yang, P. Zhang, J. Pang, B. Li and H. C. Zhou, *Chem. Commun.*, 2019, 55, 2023–2026.
- 13 L. Zhao, J. Gan, T. Xia, L. Jiang, J. Zhang, Y. Cui, G. Qian and Z. Yang, J. Mater. Chem. C, 2019, 7, 897–904.
- 14 J. Chen, Y. Wang, C. Wang, R. Long, T. Chen and Y. Yao, *Chem. Commun.*, 2019, 55, 6817–6826.
- 15 T. Ogoshi, R. Sueto, M. Yagyu, R. Kojima, T. Kakuta, T. A. Yamagishi, K. Doitomi, A. K. Tummanapelli, H. Hirao, Y. Sakata, S. Akine and M. Mizuno, *Nat. Commun.*, 2019, 10, 479.
- 16 N. Huang, P. Wang, M. A. Addicoat, T. Heine and D. Jiang, Angew. Chem., Int. Ed., 2017, 56, 4982–4986.
- 17 Q. Xu, S. Tao, Q. Jiang and D. Jiang, J. Am. Chem. Soc., 2018, 140, 7429-7432.
- 18 X. Chen, Y. Li, L. Wang, Y. Xu, A. Nie, Q. Li, F. Wu, W. Sun, X. Zhang, R. Vajtai, P. M. Ajayan, L. Chen and Y. Wang, *Adv. Mater.*, 2019, 31, 1901640–1901648.
- 19 Y. Hu, N. Dunlap, S. Wan, S. Lu, S. Huang, I. Sellinger, M. Ortiz, Y. Jin, S. H. Lee and W. Zhang, *J. Am. Chem. Soc.*, 2019, 141, 7518–7525.
- 20 L. Zhai, W. Wei, B. Ma, W. Ye, J. Wang, W. Chen, X. Yang, S. Cui, Z. Wu, C. Soutis, G. Zhu and L. Mi, ACS Mater. Lett., 2020, 2, 1691–1697.
- 21 T. Ogoshi, S. Fujinami, T. Yamagishi and Y. Nakamoto, *J. Am. Chem. Soc.*, 2008, **130**, 5022–5023.
- 22 T. Ogoshi, T. A. Yamagishi and Y. Nakamoto, *Chem. Rev.*, 2016, **116**, 7937–8002.
- 23 T. Ogoshi, T. Kakuta and T. A. Yamagishi, *Angew. Chem., Int. Ed.*, 2019, **58**, 2197–2206.
- 24 Z. Zhang, Y. Luo, J. Chen, S. Dong, Y. Yu, Z. Ma and F. Huang, *Angew. Chem., Int. Ed.*, 2011, **50**, 1397–1401.
- 25 G. Yu, M. Xue, Z. Zhang, J. Li, C. Han and F. Huang, J. Am. Chem. Soc., 2012, 134, 13248–13251.
- 26 G. Yu, C. Han, Z. Zhang, J. Chen, X. Yan, B. Zheng, S. Liu and F. Huang, J. Am. Chem. Soc., 2012, 134, 8711–8717.
- 27 M. Pan and M. Xue, Chin. J. Chem., 2014, 32, 391-395.
- 28 L. L. Tan, H. Li, Y. Tao, S. X. Zhang, B. Wang and Y. W. Yang, *Adv. Mater.*, 2014, **26**, 7027–7031.
- 29 Y. Zhou, Y. Yao and F. Huang, Chin. J. Chem., 2015, 33, 356-360.
- 30 D. Dai, J. Yang, Y. C. Zou, J. R. Wu, L. L. Tan, Y. Wang, B. Li, T. Lu, B. Wang and Y. W. Yang, *Angew. Chem., Int. Ed.*, 2021, 60, 8967–8975.
- 31 Z. Li, X. Li and Y. W. Yang, *Small*, 2019, **15**, 1805509–1805519.
- 32 Z. Li and Y.-W. Yang, Polym. Chem., 2021, 12, 4613-4620.
- 33 T. Ogoshi, Y. Shimada, Y. Sakata, S. Akine and T. A. Yamagishi, *J. Am. Chem. Soc.*, 2017, **139**, 5664–5667.
- 34 D. Xia, L. Wang, X. Lv, J. Chao, X. Wei and P. Wang, *Macromolecules*, 2018, **51**, 2716–2722.
- 35 T. Ogoshi, Y. Hamada, R. Sueto, R. Kojima, F. Sakakibara, Y. Nagata, Y. Sakata, S. Akine, T. Ono, T. Kakuta and T. Yamagishi, *Cryst. Growth Des.*, 2020, **20**, 7087–7092.

- 36 J. M. Seo, H. J. Noh, H. Y. Jeong and J. B. Baek, *J. Am. Chem. Soc.*, 2019, **141**, 11786–11790.
- 37 Y. Guan, M. Ni, X. Hu, T. Xiao, S. Xiong, C. Lin and L. Wang, *Chem. Commun.*, 2012, **48**, 8529–8531.
- 38 X.-Y. Hu, P. Zhang, X. Wu, W. Xia, T. Xiao, J. Jiang, C. Lin and L. Wang, *Polym. Chem.*, 2012, 3, 3060–3063.
- 39 T. Ogoshi, T. Aoki, S. Ueda, Y. Tamura and T. A. Yamagishi, *Chem. Commun.*, 2014, **50**, 6607–6609.
- 40 L. Wu, Y. Fang, Y. Jia, Y. Yang, J. Liao, N. Liu, X. Yang, W. Feng, J. Ming and L. Yuan, *Dalton Trans.*, 2014, 43, 3835–3838.
- 41 G. Yu, R. Zhao, D. Wu, F. Zhang, L. Shao, J. Zhou, J. Yang, G. Tang, X. Chen and F. Huang, *Polym. Chem.*, 2016, 7, 6178–6188.
- 42 X. S. Du, C. Y. Wang, Q. Jia, R. Deng, H. S. Tian, H. Y. Zhang, K. Meguellati and Y. W. Yang, *Chem. Commun.*, 2017, 53, 5326–5329.
- 43 R. Wang, Y. Sun, F. Zhang, M. Song, D. Tian and H. Li, *Angew. Chem., Int. Ed.*, 2017, **56**, 5294–5298.
- 44 Z. Zhang, L. Shao, Y. Zhou and J. Yang, *Polym. Chem.*, 2017, 55, 3529–3533.
- 45 C. Li, K. Han, J. Li, H. Zhang, J. Ma, X. Shu, Z. Chen, L. Weng and X. Jia, *Org. Lett.*, 2011, **14**, 43–45.
- 46 S. Song, Y. Shi, N. Liu and F. Liu, ACS Appl. Mater. Interfaces, 2021, 13, 10513-10523.
- 47 K. Jie, Y. Zhou, Q. Sun, B. Li, R. Zhao, D. E. Jiang, W. Guo, H. Chen, Z. Yang, F. Huang and S. Dai, *Nat. Commun.*, 2020, 11, 1086.
- 48 Z. Li, J. Yang, G. Yu, J. He, Z. Abliz and F. Huang, *Org. Lett.*, 2014, **16**, 2066–2069.
- 49 X. Chi, X. Ji, L. Shao and F. Huang, *Macromol. Rapid Commun.*, 2017, **38**, 1600626–1600632.
- 50 Y. Sun, W. Fu, C. Chen, J. Wang and Y. Yao, *Chem. Commun.*, 2017, 53, 3725–3728.
- 51 X. Mao, T. Liu, J. Bi, L. Luo, D. Tian and H. Li, *Chem. Commun.*, 2016, 52, 4385-4388.
- 52 L. Luo, G. Nie, D. Tian, H. Deng, L. Jiang and H. Li, *Angew. Chem., Int. Ed.*, 2016, 55, 12713–12716.
- 53 A. Giri, A. Sahoo, T. K. Dutta and A. Patra, *ACS Omega*, 2020, 5, 28413–28424.
- 54 S. V. Athare and S. P. Gejji, J. Mol. Model., 2019, 26(3), 3-14.
- 55 S. V. Athare and S. P. Gejji, *ChemistrySelect*, 2019, **4**, 9354–9359.
- 56 C. F. Matta, J. Hernandez-Trujillo, T. H. Tang and R. F. Bader, *Chemistry*, 2003, **9**, 1940–1951.
- 57 L. L. Tan, Y. Zhu, H. Long, Y. Jin, W. Zhang and Y. W. Yang, *Chem. Commun.*, 2017, 53, 6409–6412.
- 58 Z. Zhang, S. B. Peh, Y. Wang, C. Kang, W. Fan and D. Zhao, Angew. Chem., Int. Ed., 2020, 59, 18927–18932.
- 59 F. Yu, B.-Q. Hu, X.-N. Wang, Y.-M. Zhao, J.-L. Li, B. Li and H.-C. Zhou, J. Mater. Chem. A, 2020, 8, 2083–2089.
- 60 B. Zhu, J. W. Cao, S. Mukherjee, T. Pham, T. Zhang, T. Wang, X. Jiang, K. A. Forrest, M. J. Zaworotko and K. J. Chen, *J. Am. Chem. Soc.*, 2021, 143, 1485–1492.