




Showcasing research from Laboratories of Analytical Chemistry, and Materials Chemistry, Department of Applied Chemistry, Faculty of Science and Technology, Keio University, Yokohama, Japan.

A biomimetic hybrid material consisting of CaCO_3 mesoporous microspheres and an alternating copolymer for reversed-phase HPLC

Inspired by CaCO_3 based biominerals like eggshells, alternating amphiphilic copolymer-modified monodisperse mesoporous CaCO_3 microspheres were applied as a HPLC stationary phase for analyses of basic drugs requiring alkaline mobile phases.

As featured in:

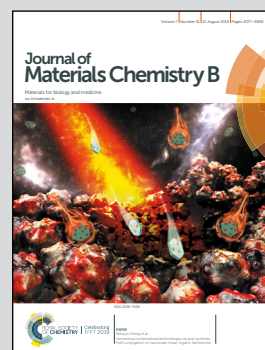

See Yuki Hiruta *et al.*,
J. Mater. Chem. B, 2019, 7, 4771.



Cite this: *J. Mater. Chem. B*, 2019, 7, 4771

A biomimetic hybrid material consisting of CaCO₃ mesoporous microspheres and an alternating copolymer for reversed-phase HPLC†

Mai Mochida, Yuta Nagai, Hiroto Kumagai, Hiroaki Imai,  Daniel Citterio  and Yuki Hiruta *

We developed a biomineral-inspired hybrid material composed of CaCO₃ and an organic polymer as a column packing material for HPLC. This material combines a hierarchical mesoporous structure and the functionality of the polymer. The surface of monodispersed mesoporous CaCO₃ microspheres was modified with poly(maleic acid-*alt*-1-octadecene) (PMAcO) comprising hydrophobic alkyl chains and anionic carboxylate groups. PMAcO adsorbed onto the surface of CaCO₃ through electrostatic interaction between Ca²⁺ sites and carboxylate groups, resulting in an octadecene coated microsphere interface. These microspheres were applied as a HPLC column and exhibited reversed-phase retention behavior in the separation of alkylbenzenes. This column showed high alkaline mobile phase resistance compared with the conventionally applied ODS column packing material. Quantitative analysis of the basic antidepressants clomipramine and imipramine spiked into whole blood was achieved with an alkaline mobile phase, demonstrating the potential of the biomineral-inspired material as a HPLC stationary phase for practical applications in routine analyses of basic drugs requiring alkaline mobile phases.

Received 20th May 2019,
Accepted 8th July 2019

DOI: 10.1039/c9tb01014a

rsc.li/materials-b

Introduction

Biominerals are inorganic–organic hybrid materials with hierarchically organized structures from nanoscopic to macroscopic scales.¹ For example, eggshells, seashells and corals have meso-structures of CaCO₃ nanocrystals, which are elaborately controlled by biopolymers.^{2,3} Focusing on eggshells as an example, their structure has pores that are necessary for gas exchange allowing respiration, and the presence of biopolymers prevents virus invasion. Furthermore, they provide relatively high mechanical strength to protect the inner shell.⁴ These characteristics of hierarchical structures combining CaCO₃ nanocrystals and biopolymers enable the control of substance distribution and provide mechanical strength. Therefore, material scientists have been attracted by the elaborate architecture and formation processes of these biominerals, attempting to develop new fabrication technologies and to obtain novel functionalities through imitation of these features.^{5,6}

Paying attention to the hierarchical structure of biominerals to control the distribution of substances, a normal phase chromatography stationary phase based on biopolymer-removed crushed

seashells has been developed.⁷ Although it was shown that the hierarchical structure of biominerals can be applied to a chromatographic separation material, the functionality of the biopolymer of biominerals like egg shells in terms of controlling substance distribution was not fully used for separation purposes.

In order to control the morphology of CaCO₃, crystallization methods involving anionic small molecules^{8,9} or anionic polymers^{10–12} were studied by mimicking the formation process of biominerals. We have also reported that monodispersed mesoporous CaCO₃ microspheres with 20 nm mesopores and controllable particle size can be obtained by a biomimetic process.¹³ In this method, an anionic polymer, poly(sodium 4-sulfonate) (PSS), controls crystal growth (*i.e.* assemblage of 20 nm CaCO₃ nanocrystals) by electrostatic adsorption, resulting in the formation of a metastable phase vaterite crystal. In addition, we have modified these microspheres with thermo-responsive poly(*N*-isopropylacrylamide) (PNIPAAm) to transport chemical substances from an organic to an aqueous phase by temperature-switching.¹⁴ However, after modification with PNIPAAm, the inter-particle space was fully filled with the thermo-responsive polymer, resulting in the loss of the hierarchical pore structure that is important in controlling substance distribution.

Cooperative interaction between the hierarchical structure and organic molecules is important to obtain the functions of biominerals and the high mechanical strength as in the case of

Department of Applied Chemistry, Keio University, 3-14-1 Hiyoshi, Kohoku-ku, 223-8522 Yokohama, Japan. E-mail: hiruta@aplc.keio.ac.jp

† Electronic supplementary information (ESI) available: Additional material characterizations, chromatographic results. See DOI: 10.1039/c9tb01014a



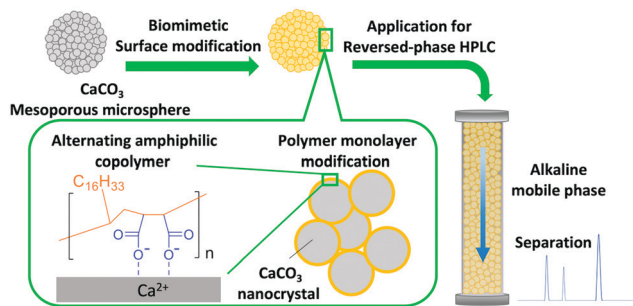


Fig. 1 Concept image.

eggshells.¹⁵ To the best of our knowledge, a biomimetic material that synergistically combines the hierarchical structure and the function of organic molecules to enable substance distribution control has not been reported. Herein, we have developed biomineral-inspired amphiphilic polymer-modified monodisperse CaCO_3 microspheres having a hierarchical pore structure and the chemical functionality of the polymer used for modification. In addition, due to the ordered assembled structures composed of polymers and abundant inorganic CaCO_3 (Fig. 1), excellent physical properties are achieved. We thought that these properties of the biomineral-inspired hybrid material are suitable for controlling substance distribution similarly to egg shells, and we applied it as a column packing material for high performance liquid chromatography (HPLC).

Column chromatography was originally developed by the botanist Mikhail Tswett, using liquid-adsorption columns containing CaCO_3 in the form of a powder of ground chalk (*i.e.* calcite crystals). This implies that synthetic CaCO_3 mesoporous microspheres are applicable as a stationary phase packing material for HPLC.¹⁶ In current HPLC columns, octadecyl silica (ODS) is the most widely used stationary phase for reversed-phase chromatography. It consists of mesoporous inorganic silica gel modified with organic hydrophobic octadecyl moieties. Because biomineral-inspired materials also possess a hierarchical mesoporous structure, their application as a reversed-phase HPLC column packing material similar to ODS is possible by hydrophobic alkyl polymer modification of their surface.

As with CaCO_3 -based biominerals wherein hierarchical structures are controlled by electrostatic adsorption between CaCO_3 crystals and biopolymers while stably maintaining the morphology,² the imitation of their formation process allows the modification of synthetic CaCO_3 mesoporous microspheres with an anionic polymer by electrostatic adsorption. By this method, mesoporous CaCO_3 particles can be stably modified, due to polymer adsorption at multiple sites on the surface of CaCO_3 , while effectively retaining the mesopores.¹⁷

In addition, CaCO_3 is stable against dissolution in alkaline solutions, since it is a basic salt. On the other hand, the use of ODS is limited due to poor hydrolytic stability against alkaline mobile phases. The fact that alkaline mobile phases have to be avoided when using low alkaline resistant silica gel column materials is a disadvantage leading to low separation performance for basic analytes.¹⁸ By replacing ODS with the polymer-modified

CaCO_3 particles, it is possible to realize an alkaline stable packing material overcoming the disadvantages of conventional stationary phases.


We have developed a biomineral-inspired inorganic-organic hybrid material by modifying the surface of monodisperse mesoporous CaCO_3 microspheres through electrostatic adsorption of a regularly alternating copolymer having both anionic groups and functional groups, while maintaining the mesoporous structure. Whereas the anionic groups serve the purpose of adsorbing the polymer to the crystal surface, the alternating functional groups impart their functionality. Thus, efficient modification and functionalization of the surface of the monodisperse mesoporous CaCO_3 microspheres were simultaneously achieved. Especially, maleic anhydride based alternating copolymers can obtain various functionality by radical copolymerization of maleic anhydride with styrene, α -olefins, or vinyl ethers.¹⁹ In this work, poly(maleic acid-*alt*-1-octadecene) (PMAO), consisting of regularly alternating hydrophobic alkyl chains and two carboxylate units, was used (Fig. 1). The presence of the octadecyl groups on the surface of the monodisperse mesoporous CaCO_3 microspheres imparts a strong hydrophobic character, similar to the octadecyl groups of ODS, and enables the application as a versatile packing material in reversed-phase HPLC.

Results and discussion

Preparation and characterization of amphiphilic polymer modified monodisperse CaCO_3 microspheres

Bare monodisperse mesoporous CaCO_3 microspheres were prepared by a simple mixing method of two solutions at room temperature according to the literature.¹³ CaCO_3 crystal growth during microsphere synthesis was controlled with PSS, followed by the decomposition of PSS using aqueous NaClO solution and calcination. PMAO was obtained by the hydrolysis of repeating maleic anhydride units in poly(maleic anhydride-*alt*-1-octadecene) (PMAO), as shown in Scheme 1.²⁰ Hydrolysis was confirmed by FT-IR spectra (Fig. S1, ESI[†]), in which the peak at 1780 cm^{-1} derived from maleic anhydride decreased, while the peak at 1729 cm^{-1} derived from maleic acid was enhanced. The surface of the bare CaCO_3 microspheres was modified with PMAO by simply dispersing the microspheres in an organic solution of PMAO. PMAO adsorbed onto the surface of CaCO_3 through electrostatic interaction between cationic calcium sites and anionic carboxylate groups, resulting in an octadecyl-coated microsphere interface referred to as " CaCO_3 -PMAO".

Particle morphologies of bare CaCO_3 and CaCO_3 -PMAO particles were observed by scanning electron microscopy (SEM),

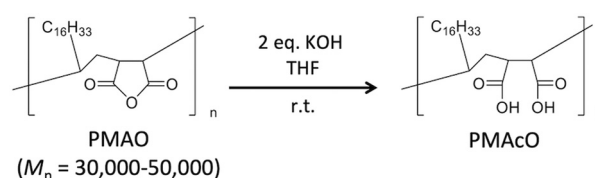

Scheme 1 Hydrolysis reaction of PMAO to form PMAO.





Fig. 2 SEM images of (A–D): bare CaCO_3 particles and (E–H): polymer-modified CaCO_3 -PMaCO particles.

as shown in Fig. 2. Both before and after modification with PMaCO, monodisperse spherical particles with identical average particle diameters of $3.5 \pm 0.4 \mu\text{m}$ and $3.5 \pm 0.6 \mu\text{m}$, respectively, were observed ($n = 400$, measured from Fig. 2D and H). The particle size distributions are shown in Fig. S2 (ESI[†]). CaCO_3 microspheres obtained by the applied synthesis method have been reported to consist of aggregates of 20 nm-sized CaCO_3 crystals,²¹ which was also observed for the modified CaCO_3 -PMaCO particles (Fig. S3, ESI[†]), confirming that the morphology of the mesoporous microspheres was retained after modification with PMaCO. According to the XRD patterns (Fig. 3A), the bare CaCO_3 particles were assigned to be pure vaterite, with the crystal structure unchanged by modification with PMaCO. FT-IR spectra (Fig. 3B) showed the appearance of peaks at 2924 and 2858 cm^{-1} derived from $-\text{CH}_2-$ moieties after modification with PMaCO. In addition, the mass reduction in

the thermogravimetric (TG) curves in the 240 – 540°C range (Fig. 3C) indicated the presence of 5 wt% PMaCO on the surface of CaCO_3 microspheres, which was comparable to oleic acid for CaCO_3 surface modification prepared in analogy to the CaCO_3 -PMaCO particles (Fig. 3D). These results demonstrate that PMaCO was successfully modified onto the surface of CaCO_3 microspheres while maintaining their properties. The pore size distributions of CaCO_3 microspheres before and after PMaCO modification were obtained by nitrogen adsorption-desorption isotherms (Fig. 3E). While the pore size distributions hardly changed upon modification with the polymer, the pore diameter decreased from 22 to 16 nm (Fig. 3F). The thickness of an octadecanoic acid monolayer on CaCO_3 has been reported to be $\approx 2.6 \text{ nm}$.²² Therefore, these results infer that a uniform monolayer of repeating octadecene units was formed on the surface of the pores by PMaCO modification. Since ODS

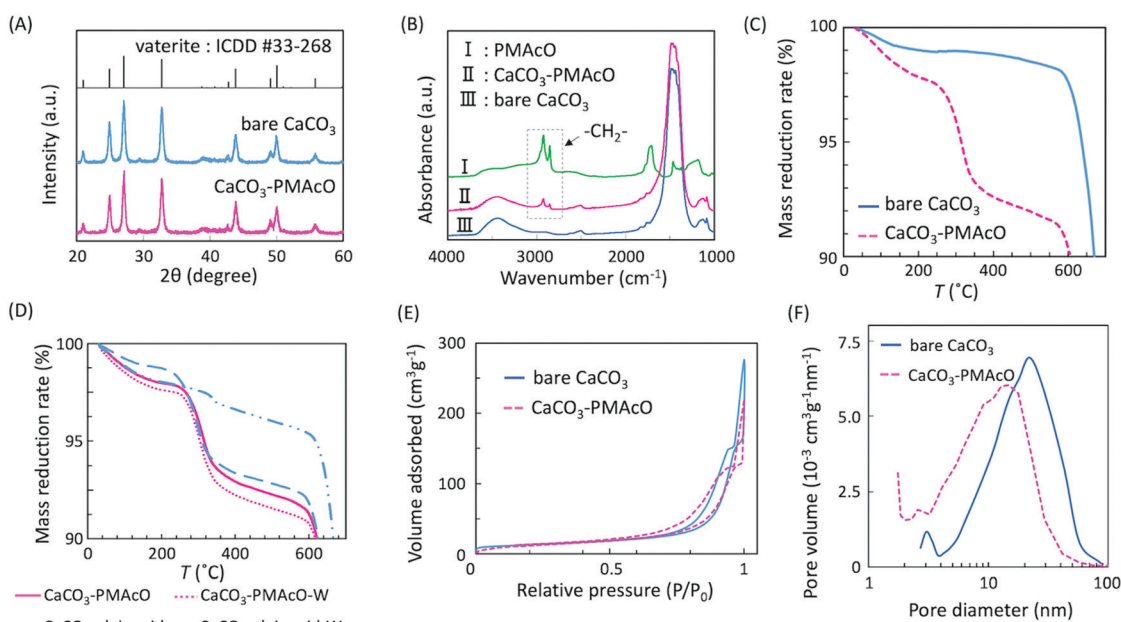


Fig. 3 Physical properties of bare CaCO_3 and CaCO_3 -PMaCO microspheres: (A) XRD spectra, (B) FT-IR spectra, (C) TG curves, (D) TG curves of CaCO_3 -PMaCO and CaCO_3 -oleic acid before and after washing; “-W” indicates samples after washing, (E) N_2 adsorption-desorption isotherms, and (F) pore size distributions.



particles used in HPLC column packings have a uniform particle size of 2–5 μm with 6–30 nm pores, the current CaCO_3 -PMAcO microspheres with comparable uniform particle size and pore size fulfil the basic requirements to be applied as a HPLC column packing material. For successful application as a packing material for long-term reproducible HPLC analysis, durability against the mobile phase solvent is required. Since the PMAcO polymer has a plurality of adsorption sites, it is expected to be stably adsorbed onto the surface of CaCO_3 . The durability of the PMAcO modification was experimentally evaluated by comparing the amount of organic components by means of the TG curves in the 240–540 $^\circ\text{C}$ regime recorded before and after washing with a water/methanol mixture (50/50, v/v) representing a common mobile phase. The results shown in Fig. 3D indicate that the amount of PMAcO did not change during the washing process. On the other hand, in a comparative experiment using oleic acid for CaCO_3 surface modification (prepared in analogy to the CaCO_3 -PMAcO particles), a drastic decrease of the organic compound from 5 to 1 wt% upon washing was observed, corresponding to an 80% reduction. This significant difference is attributed to the fact that oleic acid only has a single carboxylate residue to interact with the CaCO_3 surface, in contrast to PMAcO with multiple binding sites, leading to the higher durability of the latter. Therefore, the biomineral inspired surface modification with the polymer by interaction between polymeric functional groups and calcium sites seems to contribute to the long-term durability of CaCO_3 -PMAcO and, hence, its applicability as a packing material for HPLC.

Evaluation of CaCO_3 -PMAcO microspheres as a column packing material for HPLC

CaCO_3 -PMAcO microspheres were packed into a column (100 \times 2.1 mm I.D.) and their performance as a stationary phase for HPLC was evaluated. Fig. S4A (ESI[†]) shows the relationship between the mobile phase mixing ratio and the back pressure for methanol/water mixtures. At a flow rate of 0.4 mL min^{-1} , the back pressure of the column was below 15 MPa (Fig. S4B, ESI[†]). Furthermore, the back pressure was found to be stable and,

therefore, suitable for use with a conventional HPLC system. The separation mode of this column was evaluated through the elution behavior of naphthalene and alkylbenzenes (C0–C10) depending on the mixing ratio of methanol/water as the mobile phase. The retention factors of naphthalene and alkylbenzenes increased with decreasing proportions of methanol (Fig. S5, ESI[†] and Fig. 4A) and longer alkyl chains resulted in higher hydrophobicity (Fig. 4A). These results indicate that CaCO_3 -PMAcO behaved as a reversed-phase mode stationary phase for the separation of naphthalene and alkylbenzenes, while pure CaCO_3 generally works as normal-phase mode stationary phase.⁷ The octadecene groups of the CaCO_3 -PMAcO microspheres at the stationary phase to mobile phase interface performed a role identical to the octadecyl groups of ODS, resulting in reversed-phase characteristics. During the separation of a mixture of 11 alkylbenzenes, all peaks could be clearly observed with a baseline resolution (peak resolution $R_s = 1.8\text{--}4.2 > 1.5$) in the chromatogram (Fig. 4B).

The durability of the CaCO_3 -PMAcO column against an alkaline mobile phase (mixture of pH 10.8 aqueous $\text{Na}_2\text{B}_4\text{O}_7$ buffer and methanol) was evaluated by monitoring the elution behavior of naphthalene. The deterioration of the column was estimated by the relative change of the retention time during the continuous flow of the mobile phase. A comparative study was carried out using an ODS column prepared from a commercially available 3 μm ODS silica packing material through the same procedure as that for the CaCO_3 -PMAcO column. As shown in Fig. 4C and Fig. S6 (ESI[†]), the retention time and the number of theoretical plates of naphthalene were retained over 3500 column volumes (CVs) of alkaline mobile phase purging in the case of the CaCO_3 -PMAcO column (RSD of retention time: 0.7%), while it continuously decreased when using the ODS packed column (over 35% decrease after 3500 CV purges). It is assumed that the amount of octadecyl groups on the silica surface gradually decreased due to the inherent solubility of silica in alkaline media, resulting in a reduction of hydrophobic interaction with naphthalene. In contrast, the performance of the CaCO_3 -PMAcO packing in the alkaline mobile phase was preserved, since

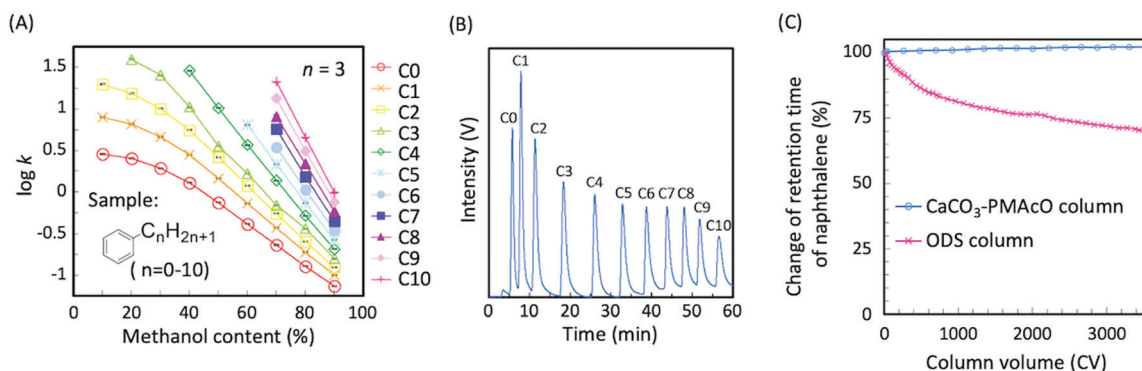


Fig. 4 (A) Retention factors of C0–C10 alkylbenzenes obtained with a CaCO_3 -PMAcO packed column. Each sample was eluted at each mixing ratio of the methanol/water mobile phase ranging from 10/90 (v/v) to 90/10 (v/v); error bars represent mean values $\pm 1\sigma$ ($n = 3$); flow rate of mobile phase 0.3 mL min^{-1} . (B) Chromatogram showing the separation of a mixture of C0–C10 alkylbenzenes by the CaCO_3 -PMAcO column. Gradient elution was applied at a flow rate of 0.1 mL min^{-1} starting with methanol/water (50/50, v/v) for 4 min, followed by the gradient program up to 80/20 (v/v) over 36 min and finally elution with 80/20 (v/v) for 20 min. (C) Relative change of the retention time of naphthalene upon continuous running of alkaline mobile phase (50/50, v/v methanol/pH 10.8 $\text{Na}_2\text{B}_4\text{O}_7$ buffer) in the case of CaCO_3 -PMAcO and ODS columns; flow rate of mobile phase 0.3 mL min^{-1} .



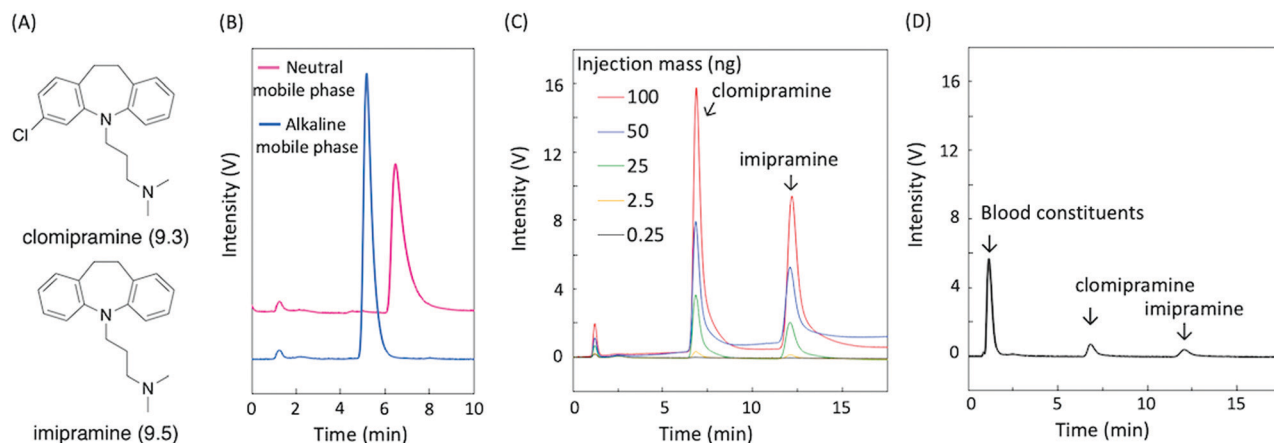


Fig. 5 (A) Chemical structures and pK_a of the basic antidepressants clomipramine and imipramine; chromatograms of basic antidepressants for the CaCO_3 -PMACo column flowed at 0.3 mL min^{-1} . (B) clomipramine (0.1 mg mL^{-1}) with neutral and alkaline mobile phases. Methanol/water (63/37, v/v) was used as a neutral mobile phase and methanol/pH 10.8 $\text{Na}_2\text{B}_4\text{O}_7$ buffer (63/37, v/v) was used as an alkaline mobile phase. (C) Mixture of two basic antidepressants (clomipramine and imipramine) with a methanol/pH 10.8 $\text{Na}_2\text{B}_4\text{O}_7$ buffer (55/45, v/v). (D) Basic antidepressants (clomipramine and imipramine) spiked into whole blood of porcine with a methanol/pH 10.8 $\text{Na}_2\text{B}_4\text{O}_7$ buffer (55/45, v/v).

the solubility of CaCO_3 decreases with increasing pH. These results indicated that CaCO_3 -PMACo packed columns show excellent durability at high pH and could be used for routine analyses requiring alkaline mobile phases.

Quantitative analysis of basic antidepressants spiked into whole blood using a CaCO_3 -PMACo packed column

As a proof-of-concept demonstration, we conducted the analysis of basic compounds requiring an alkaline mobile phase for successful separation. When a neutral mobile phase is used, basic compounds become positively charged, resulting in unwanted electrostatic and hydrogen bond interactions with the stationary phase in addition to hydrophobic interactions. On the other hand, these are eliminated by deprotonation of basic compounds in alkaline mobile phases, allowing the separation of basic compounds as free bases, which is attractive for routine analysis. Silica-based columns are reluctantly used because of their inherent instability to alkaline mobile phases.²³ Herein, we demonstrate the analysis of the basic antidepressants clomipramine and imipramine (pK_a of 9.3 and 9.5, respectively,²⁴ shown in Fig. 5A), known as tricyclics. Since addiction to psychotropic drugs is a serious problem, the routine analysis of these substances in biological fluids is of significance.²⁵ First, the effect of the mobile phase pH on the elution behavior of clomipramine using a CaCO_3 -PMACo packed column was investigated. Fig. 5B shows the chromatograms of clomipramine on a CaCO_3 -PMACo stationary phase eluted with a neutral or alkaline mobile phase. A sharper peak was obtained when using the alkaline mobile phase compared to the neutral mobile phase (1.4-fold number of theoretical plates; 0.7-fold peak asymmetry factor). Protonation of clomipramine in the neutral mobile phase resulted in the interaction with anionic carboxylates or carbonates, causing tailing and extension of the retention time. The suppression of clomipramine protonation eliminated these unwanted interactions, leading to a sharp chromatographic peak with simple retention behavior only governed by hydrophobic interactions

Table 1 Recovery of basic drugs from a whole blood sample

Basic drug	Level ($\text{ng } \mu\text{L}^{-1}$)	From peak area		From peak height	
		Recovery (%, $n = 3$)	RSD (%, $n = 3$)	Recovery (%, $n = 3$)	RSD (%, $n = 3$)
Imipramine	5.0	96.4	0.2	95.6	0.3
Clomipramine	5.0	97.6	0.7	96.2	0.7

between clomipramine and octadecene groups. In addition, clomipramine and imipramine were successfully separated by the CaCO_3 -PMACo column in combination with the alkaline mobile phase (Fig. 5C). Linear calibration curves for clomipramine and imipramine were obtained based on the peak areas or heights from chromatograms of mixed samples of the two basic antidepressants (Fig. S7A and B, ESI[†]). Finally, porcine whole blood spiked with clomipramine and imipramine was analyzed using the CaCO_3 -PMACo packed column and the alkaline mobile phase. The sample was prepared according to a general whole blood pretreatment method²⁶ before HPLC analysis. Fig. 5D shows the corresponding chromatogram. Blood constituents (mainly serum albumin) and the two basic antidepressants were successfully separated. Furthermore, good recovery values (95.6–97.6%) and small relative standard deviations ($\text{RSD} < 0.7\%$) calculated from the calibration curves (Fig. S7A and B, ESI[†]) were achieved (Table 1). On the other hand, the two basic antidepressants were not successfully separated with the ODS packed column in a neutral mobile phase (Fig. S8, ESI[†]). These results indicated that HPLC analysis with CaCO_3 -PMACo packed columns in an alkaline mobile phase is practically applicable to the routine analysis of basic antidepressants.

Conclusions

This work is to the best of our knowledge the first example of a biomimetic material in which the hierarchical structure and the polymer function are fused to enable effective control of substance distribution. By mimicking the formation process of



biominerals, mesoporous CaCO_3 microspheres were fabricated and surface-modified with an alternating amphiphilic copolymer consisting of hydrophobic alkyl chains and anionic carboxylate groups. Because of the monodisperse and mesoporous structure modified with hydrophobic octadecene groups on its surface, this biomineral-inspired hybrid material was found to be suitable for application in HPLC. When applied as a HPLC column packing material, it showed reversed-phase retention behavior and high resistance against alkaline mobile phases. In a proof-of-concept application, whole blood spiked with basic antidepressants clomipramine and imipramine was successfully analyzed with an alkaline mobile phase, in which conventional ODS packings have significant stability limitations. Thus, the present work clearly demonstrates the potential of biomineral-inspired PMAcO-modified mesoporous CaCO_3 microspheres as a HPLC column packing material. By decreasing the particle size of the mesoporous CaCO_3 microspheres, the pore size distribution can be narrowed. Furthermore, since decreasing the particle diameter leads to an expansion of the specific surface area and an improvement of packing density, it is expected that a higher separation ability can be obtained by decreasing the particle diameter. Furthermore, it is expected that various retention modes can be imparted to this packing material with a variety of maleic acid-based alternating polymers. Therefore, we expect that this work opens a new route for biomimetic materials in separation applications.

Experimental section

Materials and instruments

Calcium chloride (CaCl_2), sodium carbonate (Na_2CO_3), 5 wt% aqueous sodium hypochlorite (NaClO) solution, tetrahydrofuran (THF) and HPLC-grade methanol were purchased from Kanto Chemical (Tokyo, Japan). Toluene, acetone, potassium hydroxide (KOH), trifluoroacetic acid (TFA), oleic acid, sodium tetraborate decahydrate ($\text{Na}_2\text{B}_4\text{O}_7 \cdot 10\text{H}_2\text{O}$), sodium hydroxide (NaOH), naphthalene and clomipramine hydrochloride were purchased from Wako Pure Chemical (Osaka, Japan). Poly(sodium 4-sulfonate) (PSS, M_w : $\sim 70\,000$) and poly(maleic anhydride-*alt*-1-octadecene) (PMAO, M_n : 30 000–50 000) were purchased from Sigma-Aldrich (St. Louis, MO). Benzene, methylbenzene, ethylbenzene, amylbenzene, butylbenzene, hexylbenzene, heptylbenzene, *n*-octylbenzene, nonylbenzene, decylbenzene and imipramine hydrochloride were purchased from Tokyo Chemical Industry (Tokyo, Japan). A 3 μm fully porous ODS silica gel (CHEMCOSORB 3-ODS-L) was purchased from Chemco Scientific (Osaka, Japan). Porcine whole blood with 0.3 wt% citric acid was purchased from Tokyo Shibaura Zouki CO (Tokyo, Japan). Ultrapure water (18.2 M Ω cm) was obtained from a PURELAB flex water purification system (ELGA, Veolia Water, Marlow, U.K.).

Fabrication of CaCO_3 microspheres

128 mL of 1 M CaCl_2 solution was added to 4.0 mL of 16 mM Na_2CO_3 solution containing 1.0 g L $^{-1}$ PSS. After mixing, the solution was stirred at 1500 rpm for 90 s with a discoid shape

magnetic stirrer tip (diameter: 30.5 mm, and height: 12 mm) and then left for 24 h. After filtration, the organic components included in the products were extracted by immersion in 5 wt% NaClO aqueous solution for 48 h. The resultant microspheres were washed extensively with purified water and annealed at 400 $^\circ\text{C}$, leading to bare CaCO_3 microspheres.

Preparation of PMAcO by hydrolysis of PMAO

315 mg of solid KOH was added into 10 mL of a solution of 1.0 g of PMAO in THF, followed by vigorous stirring for 2 hours at room temperature. After evaporating the solvent, the residue was dissolved in a small amount of acetone, and an excess amount of TFA was added. Aggregates were re-dissolved in 5 mL of acetone and slowly poured into 100 mL of water to precipitate the polymer. This purified polymer was collected by suction filtration with water washing and dried in a vacuum.

Modification of PMAcO onto the surface of CaCO_3 microspheres

100 mg of PMAcO was dissolved in 20 mL of THF and 30 mL of toluene. After addition of 1.0 g of bare CaCO_3 microspheres, stirring was vigorously continued for 2 hours at 60 $^\circ\text{C}$. The collected " CaCO_3 -PMAcO" microspheres were washed with a small amount of THF and dried at 60 $^\circ\text{C}$. Oleic acid-modified CaCO_3 microspheres were obtained by the same procedure. 100 mg of oleic acid was dissolved in 50 mL of toluene. After addition of 1.0 g of bare CaCO_3 microspheres, stirring was vigorously continued for 2 hours at 60 $^\circ\text{C}$. The collected " CaCO_3 -oleic acid" microspheres were washed with a small amount of THF and dried at 60 $^\circ\text{C}$.

Characterization of PMAcO, CaCO_3 particles and modified CaCO_3 particles

The morphologies of bare CaCO_3 and CaCO_3 -PMAcO were observed using scanning electron microscopy (SEM, S-4700, Hitachi, Tokyo, Japan). Before observation, samples were coated with osmium using an osmium coater (HPC-1S, Vacuum Device, Ibaraki, Japan) for 15 s at 10 mA. For the observation of fractured CaCO_3 -PMAcO, the sample was prepared by a thick coating with osmium using an osmium coater for 60 s at 10 mA, followed by crushing with a microspatula. The size of microspheres was measured using the image processing software ImageJ (National Institutes of Health). The Brunauer-Emmett-Teller (BET) surface area, pore volume and pore size distributions were determined by N_2 sorption (3Flex, Micromeritics, SHIMADZU, Kyoto, Japan). Before measurements, samples were degassed for 6 h at 160 $^\circ\text{C}$. The crystal structures of the samples were confirmed by X-ray diffraction (XRD, MiniFlex II diffractometer, Rigaku, Tokyo, Japan) using $\text{CuK}\alpha$ radiation. Organic components of samples were also characterized using high throughput Fourier transform infrared spectroscopy (FT-IR, model-Alpha, Bruker, Germany). The contents of organic components of microspheres were measured by thermogravimetric analysis (TG, TG/DTA7200, SII, Chiba, Japan). Durability of PMAcO modification was evaluated by comparing the amounts of organic components in the 240–540 $^\circ\text{C}$ regime of the TG



curves before and after washing with solvent. CaCO_3 -PMAcO was washed 10 times with 10 mL (total 100 mL) of a mixed solvent of water and methanol (50/50, v/v) with suction filtration and dried in a vacuum. CaCO_3 -oleic acid was evaluated according to the same procedure.

Column packing

A slurry of CaCO_3 -PMAcO was packed into stainless steel columns (100 mm \times 2.1 mm I.D., Chemco Scientific). The slurry of CaCO_3 -PMAcO beads (0.7 g) in methanol (13 mL) was poured into a slurry reservoir (Chemco Scientific) connected to the stainless steel column. Methanol was flowed through the slurry reservoir using a HPLC pump (LC-6AD, SHIMADZU) for 30 min, followed by flowing methanol/water (50/50, v/v) for 60 min with a constant pressure of 35 MPa. CHEMCOSORB 3-ODS-L was packed by the same procedure.

Chromatographic analyses

Chromatographic analyses were carried out using a Prominence-I LC2030C (SHIMADZU) system equipped with a UV-Vis detector. All measurements were conducted at 25 °C with 1 μL injection volume. Elution behavior of all samples was monitored at 254 nm. All samples were dissolved in methanol and filtered through a 0.2 μm membrane filter. The pH of the 50 mM $\text{Na}_2\text{B}_4\text{O}_7$ buffer was adjusted to 10.8 with 100 mM NaOH aq.

Chromatographic parameters were calculated using the following equations:

Retention factor: $k = (t_{\text{R}} - t_0)/t_0$, where t_0 and t_{R} are the retention times of solvent peak and the target analyte, respectively.

Peak resolution: $R_{\text{S}} = 2(t_{\text{R}2} - t_{\text{R}1})/(W_1 + W_2)$, where t_{R} is the retention time ($t_{\text{R}2} > t_{\text{R}1}$), W is the peak width of the analyte, and $R_{\text{S}} > 1.5$ indicates complete separation.

Theoretical plate: $N = 16(t_{\text{R}}/W)^2$

Peak asymmetry factor: $A_{\text{s}} = b/a$, where a is the time from the leading edge of the peak to the peak midpoint, and b is the time from the peak midpoint to the tailing edge.

Preparation of whole blood samples

Porcine whole blood samples were pretreated using a protein precipitation method.²⁶ To a 2 mL centrifuge tube, 200 μL of whole blood, 100 μL of basic drug mixture (50 $\mu\text{g mL}^{-1}$ imipramine, and 50 $\mu\text{g mL}^{-1}$ clomipramine in methanol) or 100 μL of methanol as a blank sample, and 700 μL of acetonitrile were added. These solutions were mixed using a vortex mixer for 10 minutes and centrifuged at 10 000 rpm for 10 minutes. The supernatant was filtered through a 0.2 μm membrane filter.

Conflicts of interest

There are no conflicts to declare.

Notes and references

- 1 S. Mann, *Nature*, 1993, **365**, 499–505.
- 2 Y. Oaki, A. Kotachi, T. Miura and H. Imai, *Adv. Funct. Mater.*, 2006, **16**, 1633–1639.
- 3 H. B. Yao, J. Ge, L. B. Mao, Y. X. Yan and S. H. Yu, *Adv. Mater.*, 2014, **26**, 163–188.
- 4 O. D. Wangenstein, D. Wilson and H. Rahn, *Respir. Physiol.*, 1970, **11**, 16–30.
- 5 S. Mann, B. R. Heywood, S. Rajam and J. D. Birchall, *Nature*, 1988, **334**, 692–695.
- 6 S. Matsumura, S. Kajiyama, T. Nishimura and T. Kato, *Small*, 2015, **11**, 5127–5133.
- 7 K. Sato, Y. Oaki, D. Takahashi, K. Toshima and H. Imai, *Chem. – Eur. J.*, 2015, **21**, 5034–5040.
- 8 S. Kim and C. B. Park, *Langmuir*, 2010, **26**, 14730–14736.
- 9 Y. Lai, L. Chen, W. Bao, Y. Ren, Y. Gao, Y. Yin and Y. Zhao, *Cryst. Growth Des.*, 2015, **15**, 1194–1200.
- 10 A. W. Xu, M. Antonietti, S. H. Yu and H. Cölfen, *Adv. Mater.*, 2008, **20**, 1333–1338.
- 11 M. Abebe, N. Hedin and Z. Bacsik, *Cryst. Growth Des.*, 2015, **15**, 3609–3616.
- 12 G. D. Profio, S. M. Salehi, R. Caliendo, P. Guccione, G. Nico, E. Curcio and E. Fontananova, *Adv. Mater.*, 2016, **28**, 610–616.
- 13 H. Imai, N. Tochimoto, Y. Nishino, Y. Takezawa and Y. Oaki, *Cryst. Growth Des.*, 2012, **12**, 876–882.
- 14 A. Inoue, H. Tamagawa, Y. Oaki, S. Aoshima and H. Imai, *J. Mater. Chem. B*, 2015, **3**, 3604–3608.
- 15 T. Kato, *Adv. Mater.*, 2000, **12**, 1543–1546.
- 16 M. Tswett, *Ber. Dtsch. Bot. Ges.*, 1906, 316–323.
- 17 J. Zhang, J. Guo, T. Li and X. Li, *Int. J. Green Nanotechnol. Phys. Chem.*, 2010, **1**, P65–P71.
- 18 H. A. Claessens and M. A. van Straten, *J. Chromatogr. A*, 2004, **1060**, 23–41.
- 19 Z. M. O. Rzaev, *Prog. Polym. Sci.*, 2000, **25**, 163–217.
- 20 W. Lee, A. R. Esker and H. Yu, *Colloids Surf., A*, 1995, **102**, 191–201.
- 21 H. Tamagawa, H. Kageyama, Y. Oaki, Y. Hoshino, Y. Miura and H. Imai, *Chem. Lett.*, 2015, **44**, 1425–1427.
- 22 P. Fenter and N. C. Sturchio, *Geochim. Cosmochim. Acta*, 1999, **63**, 3145–3152.
- 23 J. J. Kirkland, M. A. van Straten and H. A. Claessens, *J. Chromatogr. A*, 1998, **797**, 111–120.
- 24 C. Alves, C. Fernandes, A. Jose dos Santos Neto, J. C. Rodrigues, M. E. Costa Queiroz and F. M. Lancas, *J. Chromatogr. Sci.*, 2006, **44**, 340–346.
- 25 K. Kudo, T. Ishida, W. Hikiji, Y. Usumoto, T. Umehara, K. Nagamatsu, A. Tsuji and N. Ikeda, *Forensic Toxicol.*, 2010, **28**, 25–32.
- 26 A. E. Steuer, M. Poetzsch, M. Koenig, E. Tingelhoff, S. N. Staeheli, A. T. Roemmelt and T. Kraemer, *J. Chromatogr. A*, 2015, **1381**, 87–100.

