



Cite this: *Chem. Soc. Rev.*, 2021, 50, 11870

Solution-processed two-dimensional materials for next-generation photovoltaics

Sebastiano Bellani,^{id ab} Antonino Bartolotta,^c Antonio Agresti,^d Giuseppe Calogero,^{id c} Giulia Grancini,^e Aldo Di Carlo,^{id df} Emmanuel Kymakis^{id g} and Francesco Bonaccorso^{id *ab}

In the ever-increasing energy demand scenario, the development of novel photovoltaic (PV) technologies is considered to be one of the key solutions to fulfil the energy request. In this context, graphene and related two-dimensional (2D) materials (GRMs), including nonlayered 2D materials and 2D perovskites, as well as their hybrid systems, are emerging as promising candidates to drive innovation in PV technologies. The mechanical, thermal, and optoelectronic properties of GRMs can be exploited in different active components of solar cells to design next-generation devices. These components include front (transparent) and back conductive electrodes, charge transporting layers, and interconnecting/recombination layers, as well as photoactive layers. The production and processing of GRMs in the liquid phase, coupled with the ability to “on-demand” tune their optoelectronic properties exploiting wet-chemical functionalization, enable their effective integration in advanced PV devices through scalable, reliable, and inexpensive printing/coating processes. Herein, we review the progresses in the use of solution-processed 2D materials in organic solar cells, dye-sensitized solar cells, perovskite solar cells, quantum dot solar cells, and organic–inorganic hybrid solar cells, as well as in tandem systems. We first provide a brief introduction on the properties of 2D materials and their production methods by solution-processing routes. Then, we discuss the functionality of 2D materials for electrodes, photoactive layer components/additives, charge transporting layers, and interconnecting layers through figures of merit, which allow the performance of solar cells to be determined and compared with the state-of-the-art values. We finally outline the roadmap for the further exploitation of solution-processed 2D materials to boost the performance of PV devices.

Received 29th January 2021

DOI: 10.1039/d1cs00106j

rsc.li/chem-soc-rev

1. Introduction

Energy supply is one of the most pressing issues of the twenty-first century, having a harsh impact on the global economy and society.^{1–3} Unending technological development in any human activity, ranging from transport to consumers electronics (*e.g.*, cell phones, laptops, *etc.*) and even stationary applications,⁴ has led to a growing demand of cost-effective and environmentally

friendly energy conversion and storage (ECS) devices.^{5,6} In this context, photovoltaic (PV), or solar cell (SC), technology has been at the center of an ongoing research effort,^{7–10} due to the direct exploitation of energy from sunlight, which can significantly contribute toward energy conversion in a sustainable and economical way.¹¹ Basically, SCs are electrical devices that use the PV effect to convert energy of light directly into electricity.^{7–12} Thus, SCs require a light-harvesting material that absorbs photons and raises electrons from their molecular/atomic orbitals to generate free electron (e^-)/hole (h^+) pairs *via* the PV effect.^{13,14} Once excited, charge carriers can either dissipate the energy as heat and recombine into their initial energy state or travel through the cell structure until they reach their respective electrodes.¹⁵ In building the SC structure, a built-in potential barrier (ideally corresponding to the open circuit voltage V_{OC}) is typically created to act on the free charges, driving current through an external circuit, thereby powering desired loadings.^{16,17}

The maximum theoretical solar-to-electrical energy conversion efficiency (η_{th}) of a SC for a single p–n junction ($\sim 33\%$ for 1 sun illumination) is determined by the Shockley–Queisser

^a BeDimensional S.p.A., Via Lungotorrente Secca 30R, 16163 Genova, Italy.

E-mail: f.bonaccorso@bedimensional.it

^b Istituto Italiano di Tecnologia, Graphene Labs, via Morego 30, 16163 Genova, Italy

^c CNR-IPCF, Istituto per i Processi Chimico-Fisici, Via F. Stagno D'alcontres 37, 98158 Messina, Italy

^d CHOSE – Centre for Hybrid and Organic Solar Energy, University of Rome “Tor Vergata”, via del Politecnico 1, 00133 Roma, Italy

^e University of Pavia and INSTM, Via Taramelli 16, 27100 Pavia, Italy

^f L.A.S.E. – Laboratory for Advanced Solar Energy, National University of Science and Technology “MISiS”, 119049 Leninskiy Prospekt 6, Moscow, Russia

^g Department of Electrical & Computer Engineering, Hellenic Mediterranean University, Estavromenos 71410 Heraklion, Crete, Greece



(S-Q) thermodynamic limit.¹⁸ In agreement with the S-Q limit, the charge carriers generated by photons with energies (E_{ph}) larger than the semiconductor bandgap (E_{g}) lose their excess energy ($= E_{\text{ph}} - E_{\text{g}}$) as heat through the excitation of lattice vibrations.¹⁸ Since the energy conversion efficiency (η), *i.e.*, the fraction of incident power that is converted into electricity, remains one of the most critical parameters to optimize SCs for implementation, several approaches to overcome the S-Q limit have been proposed. Some examples include tandem cells (multiple p-n junctions),^{19–21} hot-carrier SCs,^{22,23} SCs generating multiple e^-/h^+ pairs for a single incident phonon,^{24–26} and multi-band and impurity SCs.^{27,28}

To improve commercially available SCs with respect to both performance and cost-effectiveness, several potential photo-active materials are under investigation. So far, doped forms of single- or polycrystalline Si (*i.e.*, 1st-generation SCs) have comprised the lion's share of SCs in the PV market.^{29,30} In fact, they achieved η superior to 25%,^{31,32} up to a record value of 26.7%.³³ The latter was demonstrated in a heterojunction with intrinsic thin-layer technology (HIT) based on thin amorphous Si (a-Si) passivating layers and on interdigitated back contacts on n-type Si wafers.³³ Subsequently, thin-film solar cells (TFSCs, *i.e.*, 2nd-generation SCs), based on “thin” films having a thickness of $\sim 1\text{--}2\ \mu\text{m}$, have played an important role in the



Sebastiano Bellani

Sebastiano Bellani is a researcher at BeDimensional S.p.A. He received his PhD from Politecnico di Milano, while working at the Istituto Italiano di Tecnologia. Here, he investigated solid/liquid interfaces in organic semiconductor water-gated organic field-effect transistors, hybrid organic-inorganic photoelectrochemical cells, and biopolymer-based devices for optical cellular stimulation. Currently, he is participating at the European Commission's Future and

Emerging Technology Graphene Flagship. He has been the deputy leader of Graphene Flagship's Solar Farm Spearhead Project. His studies are focused on chemical-physical, spectroscopic, and photoelectrochemical characterizations of solution-processed two-dimensional materials and their energy-related applications including photovoltaics, (photo)-electrocatalysis, and energy storage systems.



Antonino Bartolotta

Antonino Bartolotta is a researcher at the Institute for the Chemical Physical Processes of the Italian National Research Council (CNR-IPCF). He gained his degree in chemistry from the University of Messina in Italy. His scientific activity started in the field of condensed matter physics, mainly devoted to glass transition and dynamical processes in disordered systems (glasses, polymers, and vitreous ionic conductors). Currently, his research is focused in

the field of nanomaterials and energy conversion and storage devices. He has been involved in several research projects, and he is the author/co-author of many publications in international peer-reviewed journals and book chapters.



Antonio Agresti

Antonio Agresti is an Assistant Professor at the Department of Electronic Engineering at the University of Rome Tor Vergata since 2016. His research activity mainly involves the design, engineering, fabrication, and electrical/spectroscopic characterization of hybrid and organic solar cells; use of graphene and transition metal dichalcogenides and emerging two-dimensional materials such as MXenes for perovskite solar cells, tandem

devices, large-area modules, and panels. He has authored/co-authored more than 50 publications and has participated as an invited speaker to several conferences in the renewable energy field. He is currently the deputy leader of Horizon 2020 Spearhead 5—Graphene Core 3 project.



Giuseppe Calogero

Giuseppe Calogero is a researcher at the Institute for the Chemical Physical Processes of the Italian National Research Council (CNR-IPCF), Messina, and he works in the field of energy and electron transfer processes. His research activity has mainly focused on the manufacturing, study, and characterization of dye-sensitized solar cells (DSSCs). He has synthesized supramolecular complexes based on polypyridine metal complexes and developed

new nanostructured materials for DSSC applications, with focus on design, preparation, and processing. He has authored over 60 articles in peer-reviewed international journals.



field of PV with regard to both η ($>22\%$)^{34,35} and cost-effectiveness.³⁶ Second-generation SCs are based on a large variety of semiconductor materials, including crystalline (c-Si)³⁷ and a-Si,³⁸ as well as GaAs³⁹ and metal chalcogenides, such as CdTe,⁴⁰ copper indium gallium diselenide ($\text{CuIn}_{1-x}\text{Ga}_x\text{Se}_2$ or CIGS),^{41,42} copper indium gallium selenide sulfide $\text{Cu}(\text{In,Ga})(\text{Se,S})_2$ (CIGSSe),³⁴ CdTe/CdS or CdS/PbS heterojunctions,^{43,44} and $\text{Cu}_2\text{ZnSnSe}_4$ (CZTSe).⁴⁵ Thin-film solar cells are characterized by some peculiar (opto)electronic

features, such as nearly ideal E_g for sunlight absorption (~ 1.4 eV, according to the S-Q limit for single-junction SCs⁴⁶) and absorption coefficient (α) ($\geq 10^5 \text{ cm}^{-1}$) over a wide spectral range (Fig. 1a and inset panel).^{47,48} For example, CdTe has E_g of 1.44 eV and α of $\sim 1.115 \times 10^6 \text{ cm}^{-1}$, while CIGS has E_g in the 1.0–1.6 eV range and $\alpha > 1 \times 10^5 \text{ cm}^{-1}$.⁹ In addition, both materials are direct-bandgap semiconductors, which implies that they can efficiently absorb above- E_g light with a thin-film layer ($\sim 1\text{--}2 \mu\text{m}$).⁴⁹ Based on the aforementioned



Giulia Grancini

Giulia Grancini is an Associate Professor in Chemistry at the University of Pavia, leading the PVsquared2 team and the ERC Project “HYNANO” aiming at the development of advanced hybrid perovskites solar cells. She obtained her PhD in Physics from Politecnico di Milano in 2012 and worked as a Post-Doc Researcher at IIT, Milano. From 2015 to 2019, she joined the École Polytechnique Fédérale de Lausanne awarded by SNSF with the Ambizione Energy Grant. In 2020, she won the Journal of Materials Chemistry Lectureship. She is currently the USERN Ambassador for Italy and a board member of the Young Academy of Europe. In 2019 and 2020, she appeared among highly cited scientists. In 2020, she was listed in “100 Experts,” which identified the top Italian women scientists in STEM. She is the author of 94 publications and owns 2 patents.



Aldo Di Carlo

Aldo Di Carlo is a Full Professor at the University of Rome Tor Vergata and Director of the Institute of Structure of Matter of the National Research Council. His research activity mainly involves the design, fabrication, and characterization of solution-processed solar cells and other optoelectronic devices. He was the founder of the Centre for Hybrid and Organic Solar Energy (CHOSE), which involved more than 35 researchers. He was the CTO of Dyepower, a consortium for the industrialization of dye solar cells for façade applications. He has authored/co-authored more than 400 publications, review articles, and book chapters, and he owns 13 patents.



Emmanuel Kymakis

Emmanuel Kymakis is a Full Professor at the Department of Electrical and Computer Engineering at the Hellenic Mediterranean University (HMU) and Vice President of the HMU Research Center. He obtained his PhD in engineering from the University of Cambridge in 2003. His research focuses on graphene and related 2D materials with regard to the interfacial engineering of emerging solar cells for improved performance and stability, as well as on the performance evaluation of PV systems. He was named as a ChemComm Emerging Investigator and served as a member of the founding GA of HFRI. He is the leader of the Energy Generation WP of the FET Flagship Initiative, Graphene Flagship.



Francesco Bonaccorso

Francesco Bonaccorso is the Founder and Scientific Director of BeDimensional S.p.A. and Visiting Scientist at the Istituto Italiano di Tecnologia. He gained his PhD from the University of Messina after working at the Italian National Research Council, the University of Cambridge, and the University of Vanderbilt. In 2009, he was awarded a Royal Society Newton International Fellowship at Cambridge University, and a Fellowship at Hughes Hall, Cambridge, receiving his MA. He was responsible in defining the ten years scientific and technological roadmap for the Graphene Flagship. He is now the deputy of the Innovation of Flagship. He was featured as 2016 Emerging Investigator by Journal of Materials Chemistry A and in 2019, by ChemPlusChem. His research interests encompass both fundamental understanding and solution processing of novel nanomaterials and their technological applications. He has authored/co-authored more than 160 publications and owns 13 patents.





Fig. 1 (a) Light wavelength (λ) dependence of the absorption coefficient (α) at room temperature (RT) of some semiconductor materials used in PV technologies. The inset shows the maximum theoretical solar-to-energy conversion efficiency (η_{th}) of SCs under AM 1.5 light radiation determined by the S–Q limit. Adapted from: ref. 47 and 48. (b) Description of the development of laboratory SCs. Inset: Cumulative installed PV capacity and plausible projection in the near future. Adapted from: ref. 63, 64 and 65.

(opto)electronic properties, CdTe and CIGS TFSCs reached η exceeding 19%³¹ and 22%,⁵⁰ respectively, thus competing with mainstream c-Si-based technology. Beyond 1st- and 2nd-generation SCs, new potential PV technologies—most of which are based on thin films—have also emerged as the 3rd-generation SCs. These include organic solar cells (OSCs),⁵¹ dye-sensitized solar cells (DSSCs),^{52–54} quantum dot solar cells (QDSCs),^{55–57} organic–inorganic hybrid SCs,^{58,59} and perovskite solar cells (PSCs).^{60–62} Organic solar cells are based on conjugated polymers or small molecules for light absorption and charge transport,⁵¹ DSSCs use an electrolyte as the charge transporting medium,^{52–54} QDSCs exploit solution-processed nanocrystals (quantum dots (QDs)) as the light-harvesting material,^{55–57} hybrid SCs mix both organic and inorganic materials as the photoactive component,^{58,59} and PSCs are based on organic–inorganic halide perovskites material (e.g., CH₃NH₃PbX₃, where X = Cl, Br, I or their mixture) as the photosensitizer.^{60–62}

The growth of the global market share of PV technology has been impressive and the demand for cumulative solar PV electricity generation is expected to move toward the scale of hundreds of gigawatts in the near future (Fig. 1b),^{63–65} with η of 2nd- and 3rd-generation SCs surpassing that of c-Si (Fig. 1b, inset panel).

Fundamentally, an ideal photoactive material for SCs based on thin films has to be a direct-bandgap semiconductor with an E_g in the 1.0–2.0 eV range to absorb sunlight in a wide spectrum range.⁴⁶ Moreover, it should have high charge carrier mobility (μ)⁶⁶ and should be compatible with one or the other material constituting the cell architecture to form reliable electrical connections.⁶⁷ Notably, the optical penetration depth (δ_p), (i.e., the spatial region in which most of the incoming photons are absorbed to produce charge carrier pairs) of the photoactive material is crucial to determine its thickness (t). In fact, δ_p can be approximated to α^{-1} , in agreement with the Lambert–Beer

law: $T_r = (I/I_0) \cdot e^{-\alpha t}$, in which T_r is the optical transmission, while I and I_0 are the intensity of transmitted and incident light, respectively.⁶⁸ Consequently, the most appropriate t value of the photoactive material should be as close as possible to the value of α^{-1} , to facilitate charge transport toward the external circuitry, without significant charge recombination losses.

Following the research effort on graphene,^{69,70} the development of other layered two-dimensional (2D) materials (named graphene-related materials (GRMs)),^{71,72} as well as other 2D materials (e.g., nonlayered 2D materials and 2D perovskites), has burgeoned into the field of SCs and optoelectronic applications. In particular, graphene opens endless possibilities for new generations of SCs owing to its outstanding (opto)electronic properties (e.g., low sheet resistance ($R_s \approx 6.45 \text{ k}\Omega \square^{-1}$),⁷³ excellent optical transparency in the UV-to-IR region ($T_r > 97.7\%$),⁷³ high intrinsic strength ($\sim 130 \text{ GPa}$), high Young modulus ($\sim 1 \text{ TPa}$), high electron mobility (μ_e) ($> 10^5 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$),⁷¹ large specific surface area (SSA) ($\sim 2630 \text{ m}^2 \text{ g}^{-1}$),⁷⁴ and excellent chemical stability and catalytic activity toward photo(electro)chemical cell-related redox reaction.^{75–77} Moreover, the (opto)electronic properties of graphene can be tuned *via* its chemical functionalization processes.^{78–80} In this context, graphene oxide (GO) (i.e., graphene with C–O bonds and functionalities, such as –OH, C=O, and COO– groups)^{81,82} or reduced graphene oxide (RGO),⁸³ as well as mono- and few-layered GRMs, exhibit electronic^{84–86} and optical properties^{87,88} that are complementary to the graphene ones. Among GRMs, transition metal dichalcogenides (TMDs) with the general stoichiometry of MX₂, where M is a transition element of groups IVB–VIIB and X is a chalcogen (i.e., S, Se, and Te) (Fig. 2), strongly emerged for their potential exploitation in the development of novel SCs due to their physical properties.^{89–91} For example, together with graphene and graphene derivatives, TMDs are becoming attractive candidates as electron/hole transporting materials in several types of SCs⁹²

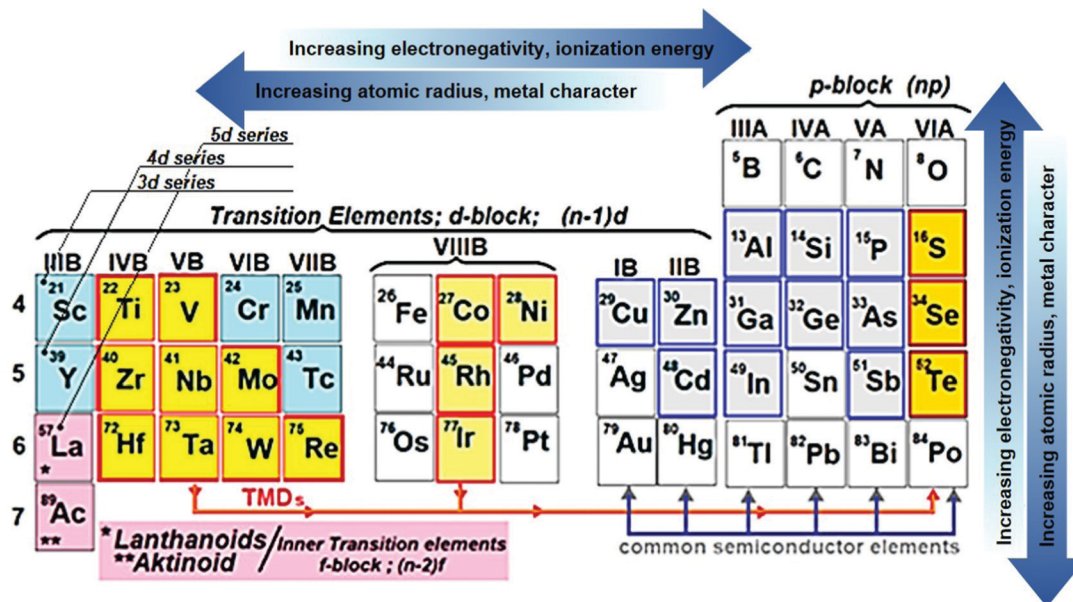


Fig. 2 Selected elements across the periodic table that—as a single element (e.g., Si, Ge), compounds (e.g., GaAs, CdAs), or alloys (e.g., $\text{Si}_x\text{Ge}_{1-x}$, $\text{Al}_x\text{Ga}_{1-x}$)—display semiconductor nature (into the blue frame) and the transition metals and three chalcogen (X) elements (enclosed by a red frame) that predominantly crystallize in layered TMDs. Partial highlights for Co, Rd, Ir, and Ni indicate that only some of their TMDs form layered structures.

due to their electronic structure capable to optimize charge transport toward the current collectors.^{93,94} Overall, the field of 2D materials is an ever-expanding research area, and new GRMs (e.g., metallic group-V TMDs,^{95,96} transition metal monochalcogenides (TMMs),^{97,98} MXenes,^{99,100} silicene,¹⁰¹ phosphorene,¹⁰² antimonene,¹⁰³ bismuthene,^{104,105} arsenene,¹⁰⁶ and graphdiyne^{107,108}) and even other types of synthetic 2D materials (not strictly belonging to the class of GRMs) are rapidly coming into the fray. Finally, the scenario of solution-processed 2D materials for PVs and, in general, optoelectronic applications, has been recently extended to both nonlayered 2D materials¹⁰⁹ and 2D perovskites.^{110,111} In their review article,¹¹² Liu *et al.* outlined the advent of 2D materials for several PV technologies, showing the most important achievements up to 2015. It is now crucial to provide an update on the use of 2D materials in SCs, including OSCs, DSSCs, PSCs, QDSCs, organic–inorganic hybrid SCs, as well as tandem systems.

The production of 2D materials by solution processing^{83,113} represents an ideal platform for the advancement of PV technologies. In fact, liquid-dispersed 2D materials can be produced with on-demand morphological properties, *i.e.*, lateral size^{114,115} and thickness^{116–118} by exploiting sorting, or can be chemically modified to tuning the (opto)electronic properties.¹¹⁹ Moreover, 2D materials produced by solution processing can be used for the realization of composites,¹²⁰ *i.e.*, blending with polymeric matrices, and the production of films by means of several coating techniques, such as inkjet^{121,122} and screen^{123,124} printing, drop¹²⁵ and dip¹²⁶ casting, and spin^{127,128} and spray^{129,130} coating.

The possibility to produce and process 2D materials and their heterostructures in the liquid phase represents a step forward toward the development of industrial-scale, reliable, inexpensive printing/coating processes, which can ultimately

lead to a reduction in the levelized cost of energy (LCOE) of current PV technologies (less than 5 US cents kW h^{-1})^{131–133} to compete with fossil fuels.^{134,135}

In this review, Section 2 provides an overview of the structural and (opto)electronic properties of 2D materials, highlighting the differences of GRMs compared to their bulk counterparts. The production and processing of GRMs in the liquid phase is thoroughly discussed in this section. A brief paragraph focuses on 2D nonlayered materials, while a specific discussion on 2D perovskites is provided in the section related to PSCs (*i.e.*, Section 6). In Section 3, we introduce the main figures of merit (FoM) of SCs and SC components to facilitate the discussion and understanding of subsequent sections. The use of solution-processed 2D materials as building blocks in OSCs, DSSCs, PSCs, and other types of SCs (*i.e.*, QDSCs and organic–inorganic hybrid SCs) is presented and critically discussed in Sections 4, 5, 6, and 7, respectively. Finally, Section 8 summarizes the key results of solution-processed 2D materials in PV technologies, providing the status, prospects, and challenges in this field.

2. Basic properties, production, and functionalization of 2D materials

2.1 Basic properties of GRMs

As depicted in Fig. 3a, graphene is a one-atom-thick layer of carbon atoms bonded together in a hexagonal honeycomb lattice.¹³⁶ Owing to its unique physical and chemical properties,⁷¹ it became highly attractive for fabricating conductive and transparent thin films,⁷³ even though numerous other (opto)electronic⁷³ and ECS^{5,137} applications exist. Graphene can be considered as the starting material for all fullerene allotropic dimensionalities,





Fig. 3 (a) Schematic of the honeycomb graphene network as formed by C atoms and bonded σ bonds perpendicular to π orbitals. The other graphene-derived allotropes of C are also shown. Adapted from ref. 139 and 140. (b) Band structure in the honeycomb lattice. In the enlarged picture, the energy bands close to one of the Dirac points are also sketched. Adapted from ref. 141.

including spherical buckyballs (zero-dimensional, 0D), one-dimensional (1D) carbon nanotubes (CNTs), further categorized in single- and multiwalled CNTs (SWCNTs and MWCNTs, respectively) depending on the number of graphene layers, as well as charcoal and graphite.¹³⁸

Graphene nanoplatelets (GNPs), *i.e.*, flakes of functionalized graphene with a thickness ranging from ~ 2 to ~ 15 nm and a lateral size ranging from the submicrometer scale to $100\ \mu\text{m}$,¹³⁷ and (R)GO, obtained by chemical/thermal processes,^{82,83} are the most frequently used graphene derivatives for large-scale industrial applications, including composites^{142–145} and ECS devices.^{5,137,142,146,147} There is a large number of studies that detail the properties of GRMs.^{71,137,148} Therefore, herein, we briefly focus only on the most peculiar properties of graphene, as well as those of other layered materials. Single-layer graphene (SLG) is a “zero-bandgap semiconductor” with the valence band (VB) and conduction band (CB) touching at the Dirac points (see Fig. 3b)^{148,149} and charge carriers that can be regarded as massless electrons or Dirac fermions.¹⁴⁸ Electron mobilities exceeding $2 \times 10^5\ \text{cm}^2\ \text{V}^{-1}\ \text{s}^{-1}$ at charge carrier densities of $\sim 2 \times 10^{11}\ \text{cm}^{-2}$ have been reported by Bolotin and co-workers by suspending SLG above a Si/SiO₂ gate electrode.¹⁵⁰ However, it has been shown that graphene on SiO₂ has a μ value that is limited by scattering from charged surface states and impurities,^{151–154} SiO₂ surface optical phonons,^{153,154} and substrate surface roughness.^{155–157} By searching for alternatives to SiO₂, it has been demonstrated that hexagonal boron nitride (h-BN), an insulating isomorph of graphite with B and N atoms and a small lattice mismatch (1.7%) relative to graphite,¹⁵⁸ represents an ideal, flat dielectric substrate for graphene.^{159,160} Thus, graphene on h-BN can reach a μ_e value exceeding $6 \times 10^5\ \text{cm}^2\ \text{V}^{-1}\ \text{s}^{-1}$,¹⁵⁹ which is 3 times higher than those shown on SiO₂. These results suggest graphene to be an ideal channel material for the fast transport of charge carriers in nanostructured and thin-film electrodes.^{161,162} As a comparison, μ of graphene is ~ 200 times higher than that of Si ($\sim 1400\ \text{cm}^2\ \text{V}^{-1}\ \text{s}^{-1}$).¹⁶³

Graphene, owing to its mechanical properties (*i.e.*, flexibility and stretchability),⁷¹ is an ideal material to fabricate flexible and ultralight devices.^{164–167} It is important to highlight the dependence of the (opto)electronic properties (*e.g.*, R_s and T_r) on the number of graphene layers. In fact, by investigating the dependence of the T_r value of graphene on the number of layers, Nair *et al.*¹⁶⁸ reported that the opacity of graphene increases by $\sim 2.3\%$ for each added layer. Moreover, Li and co-workers¹⁶⁹ measured a R_s value that varies from $2.1\ \text{k}\Omega\ \square^{-1}$ to $350\ \Omega\ \square^{-1}$, moving from SLG to 4-layer graphene, while T_r is reduced to $\sim 90\%$ (at $\lambda = 550\ \text{nm}$) for 4-layer graphene (Fig. 4).

Overall, the aforementioned properties make graphene, as well its derivatives, a distinctive material for PV applications. In fact, low R_s , large SSA, and high μ and T_r are essential requirements to be considered in the choice of material for the various building blocks of SCs. Beyond graphene, there is a plethora of other 2D materials that range from insulators (*e.g.*, h-BN) to semiconductors (*e.g.*, TMDs, such as MoS₂ and WS₂, and phosphorene), metals (*e.g.*, TiS₂ and several group-5 TMDs, such as 2H- and 3R-TaS₂, 2H- and 3R-NbS₂, and 1T-VSe₂), and even superconductors (*e.g.*, 2H-NbSe₂) and charge density wave materials (*e.g.*, 1T and 2H-TaS₂, 1T- and 2H-TaSe₂, 2H-NbSe₂, 1T-VS₂, and 1T-VSe₂) at low temperatures.^{170–173} In addition, 2D materials, such as Bi₂Te₃, Sb₂Te₃, Bi₂Se₃, SnTe, and even graphene, can display unique symmetry-protected helical metallic edge states with an insulating interior, yielding so-called topological insulators.^{174,175} As for graphene, research on other GRMs, including TMDs,^{176,177} TMMS,^{178–181} transition metal oxides (TMOs),¹⁸² monoelemental 2D materials (silicene, phosphorene, germanene, stanene, borophene, gallenene, arsenene, antimonene, bismuthene, plumbene, selenene, and tellurene),^{183,184} and MXenes,¹⁸⁵ have provided evidences that the band structure of such materials drastically changes as they shrink from the bulk to the monolayer due to quantum confinement effects.^{170,171,186} The abundance of GRMs and the ability to stack them in a layer-by-layer manner in desired sequences, eventually through solution-processed methods, offer the possibility to create novel three-dimensional (3D) architectures with entirely new functions,^{187,188} which have been foreseen to design the next generation of PV devices.¹⁸⁹ In particular, the so-formed heterostructures are held

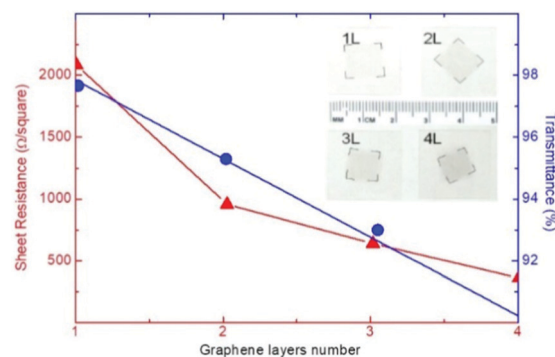


Fig. 4 Sheet resistance (R_s) and transmittance (T_r) of a graphene (film) as a function of the number of stacked graphene layers. Adapted from ref. 169. Copyright 2008, American Chemical Society.



together by van der Waals forces, as occurring in other layered materials. Since the family of GRMs is continuously expanding, the complexity of the heterostructures that can be created is nearly unlimited.¹⁹⁰ The stacking of different GRMs can lead to a series of synergistic effects, such as¹⁹⁰ (1) charge redistribution between closed materials (and even more distant materials) in the stack; (2) structural changes in the stacked materials, whose ultimate properties depend on their orientation relative to the neighboring materials. In addition to leading to the discovery and observation of novel thrilling physical phenomena, the enormous range of functionalities of 2D material heterostructures has yielded applications in PVs and optoelectronics. For example, photoactive semiconducting layers (*e.g.*, TMDs) have been coupled with graphene as transparent electrodes to form photodetectors.^{191,192} In addition, the combination of 2D materials with different work function (ϕ_w) values (such as MoS₂ and WSe₂) enables photoexcited charges (electron and holes) to be accumulated in different layers, resulting in indirect excitons with long lifetimes and tunable binding energies.^{193,194} At the atomic scale, p–n junctions (*e.g.*, GaTe/MoS₂) have been created to provide highly efficient carrier separation, reaching external quantum efficiency (EQE) higher than 60%.¹⁹⁵ The exciting and vast topic of 2D material heterostructures is subject of relevant reviews, for which we refer to more in-depth discussions.^{187,190,196–199} In the context of our work, it is worth pointing out that the realization of 2D material heterostructures with atomic precision and predetermined features by means of scalable solution-processing methods remains a formidable challenge. Nevertheless, the feasibility of printed heterostructures has been proven by several works,^{200–204} paving the way toward their integration in advanced energy conversion devices, including SCs.

It is important to point out that GRM films formed by interconnected flakes are commonly proposed as functional components in several massive applications, including energy conversion and storage applications.⁵ In fact, this approach can be realized by printing GRMs that are produced in the form of inks and pastes by means of scalable methods, such as liquid-phase exfoliation (LPE) (detailed discussion of solution-based syntheses and processing of GRMs is provided in Section 2.4).²⁰⁵ Although, in principle, the properties of each flake can be preserved, the properties of whole films strongly depends on their morphology and structure, which are determined by the orientation and interconnection between the composing flakes. The same flakes can show different lateral sizes, thicknesses, and chemical compositions (in the case of heterogeneous films), resulting in different optoelectronic characteristics.²⁰⁵ For the specific case of graphene flake films, contact resistance between the flakes and poor film compactness drastically decrease the conductivity of films compared to that of SLG and FLG ($>10\,000\text{ S cm}^{-1}$).⁶⁹ Based on our experience, an as-deposited film of pristine graphene flakes typically shows a conductivity lower than 10 S cm^{-1} , together with poor mechanical properties. In order to strengthen the interconnection among graphene flakes, the incorporation of polymeric binders and other conductive additives, *e.g.*, carbon black, is a common strategy that enables a low-temperature-processed film to achieve conductivity

higher than 100 S cm^{-1} .²⁰⁶ In particular, the use of carbon black nanoparticles (NPs) or other carbon NPs is effective to fill the voids of the as-deposited network of graphene flakes, which are consequently electrically bridged.^{206,207} The application of pressure, as well as thermal treatments, can further increase the conductivity of graphene flake films.^{208,209} In fact, compression treatments make the graphene-based films denser by decreasing the distance between flakes.²⁰⁸ Meanwhile, thermal treatments can decompose or even evaporate the binders and/or surfactants, which limit the conductivity of the film.²⁰⁹ Similar arguments apply to films composed of flakes of other GRMs besides graphene, although their functionalities can be different from those discussed above for graphene flake films.

2.2 Two-dimensional materials beyond “conventional” GRMs

2.2.1 Nonlayered materials. Beyond the class of GRMs, nonlayered materials have been created in 2D forms, raising the research interest on either fundamental research or applications in the field of optoelectronics.^{109,210–212} A comprehensive overview on the recent advancements of photoelectric devices based on 2D nonlayered materials is given in ref. 109, as well as in previous reviews.^{210–213} In the context of PV applications, nonlayered materials display fascinating properties, which can complement those of GRMs.²¹⁴ In particular, the presence of structural distortions, surface dangling bonds, and coordinated-unsaturated surface atoms can promote rapid interfacial charge transfer,²¹⁴ thereby leading to efficient charge extraction in PV devices. In addition, their chemical reactivity can be used to create *in situ* interface engineering for the design/realization of novel concepts of charge extraction.^{109,214} Example of 2D nonlayered materials are oxides/hydroxides (*e.g.*, α -FeOOH,²¹⁵ CoOOH,²¹⁵ TiO₂,²¹⁵ γ -Ga₂O₃,²¹⁶ Fe₂O₃,²¹⁷ Co₃O₄,²¹⁷ Mn₂O₃,²¹⁷ and mixed oxides such as ZnMn₂O₄ (ZMO),²¹⁷ ZnCo₂O₄,²¹⁷ NiCo₂O₄,²¹⁷ and CoFe₂O₄²¹⁷), sulfides (*e.g.*, Ga₂S₃,²¹⁸ ZnS,²¹⁵ NiS,²¹⁵ FeS₂,²¹⁹ and CuFeS₂²²⁰), selenides (*e.g.*, In₂Se₃²²¹ and ZnSe²²²), tellurides (*e.g.*, ZnTe),²²³ Ni–B oxide,²²⁴ γ -CuBr,²²⁵ CuI,²²⁶ InI,²²⁷ PbS,²¹⁵ carbonates (*e.g.*, CaCO₃, ZnCO₃, MnCO₃, FeCO₃, and PbCO₃),²¹⁵ as well as elemental Ge,²²⁸ Bi,^{229,230} Te,²³¹ and Se.²³² In this list, In₂S₃ is a direct-bandgap semiconductor in both monolayer and few-layer forms,²²¹ leading to a significantly different behavior compared to group-6 TMDs. Other 2D nonlayered materials, such as Ga₂S₃ and CuBr, exhibit bandgaps of around 3 eV,^{225,233} which is between those of group-6 TMDs and h-BN. Therefore, they can be considered as photoactive materials in the UV spectrum, as well as advanced charge-selective layers. Meanwhile, materials such as elemental ones (*e.g.*, Ge, Te, Se) or CuFeS₂ exhibit bandgaps of less than 1 eV,^{220,228,231} bridging the optical properties of graphene and the most established TMDs. Moreover, such bandgap values are attractive for the development of near-infrared (NIR) to mid-infrared (MIR) photoabsorbers. Other essential features of 2D nonlayered materials are the high tunability of their optoelectronic properties by means of engineering their surface chemical properties (*e.g.*, control of the number of vacancies in In₂S₃²³⁴ and Ga₂S₃²¹⁸), as well as theoretical high charge mobility (*e.g.*, electron mobility up to $252\,000\text{ cm}^2\text{ V}^{-1}\text{ s}^{-1}$ for PbS).²³⁵



To date, 2D nonlayered materials have been demonstrated for UV-sensitive photodetectors, reaching a responsivity of up to 3.3 A W^{-1} for Ga_2O_3 ,²³⁶ 400 A W^{-1} for $\alpha\text{-Bi}_2\text{O}_3$, and 3.17 A W^{-1} for $\gamma\text{-CuBr}$.²²⁵ In addition, visible-light photodetectors were successfully achieved using CdTe nanoflakes (responsivity of 0.6 mA W^{-1}),²³⁷ ZnTe nanoflakes (responsivity as high as 453.9 A W^{-1}),²²³ and $\alpha\text{-MnS}$ (responsivity of 139 A W^{-1}).²³⁸ PbS,²³⁹ ZnSb,²⁴⁰ and Te²³¹ nanoflakes were used for IR photo-detection, reaching responsivity of 1621 A W^{-1} , 89.2 A W^{-1} , and 13 A W^{-1} , respectively. Finally, CuGaSe_2 ,²⁴¹ $\alpha\text{-In}_2\text{Te}_3$,²⁴² $\text{Pb}_{1-x}\text{Sn}_x\text{Se}$,²⁴³ Bi,^{229,230} In_2S_3 ,²³⁴ CuInSe_2 ,²⁴⁴ Te,²⁴⁵ and Ge²²⁸ have also shown attractive properties for broadband photodetection.¹⁰⁹ Beyond the use of single 2D nonlayered materials, more complex photodetectors have been produced by coupling 2D materials, including layered and nonlayered ones, in the form of in-plane and out-of-plane heterostructures. Therefore, novel Schottky structures, p-n junctions, and phototransistors have been successfully proposed, as summarized in ref. 109. The application of 2D nonlayered materials has also been reported, although this technology is still in an early stage of development.¹⁰⁹ The progress in the control of unsaturated dangling bonds of 2D nonlayered materials is mandatory for the realization of high-quality PV devices. Recently, CdS/Cu₂S heterojunction with a clear PV effect was realized *via* the cation-exchange protocol, yielding an η value of 2.1% (despite a cell thickness of only $\sim 30 \text{ nm}$).²⁴⁶ Alternatively, GRMs have been used as an ideal interface for the growth of 2D nonlayered materials.¹⁰⁹ Based on this strategy, a PV device was fabricated by directly depositing a thin layer of MoO_3 onto MoS_2 , reaching an η value of 3.5%.²⁴⁷ Despite these progresses, the application of 2D nonlayered materials in prototypical SCs, including 1st-, 2nd-, and 3rd-generation SCs, has not been established yet, probably due to the difficulties in producing 2D nonlayered materials on a large scale.¹⁰⁹ Therefore, these materials will not be the specific subject of discussion in the present work. By achieving reproducibility in terms of thickness, crystallinity, and structural properties, their incorporation in practical PV devices could represent a key point to drive PV technologies beyond their current performances.

2.2.2 Two-dimensional conjugated metal-organic frameworks. Metal-organic frameworks are crystalline coordination polymers that have emerged for various applications (e.g., energy conversion and storage systems, proton conduction membranes, and sensors) owing to their ultrahigh porosity (up to 90% free volume) and large surface area (even beyond $6000 \text{ m}^2 \text{ g}^{-1}$).²⁴⁸ The topic of MOFs is a research hotspot in materials science, as comprehensively reviewed by several recent literature works,^{248–250} to which we specifically refer the reader of this work. As an evolution of MOFs, their 2D form, *i.e.*, 2D c-MOFs, has also been developed to extend the properties of traditional MOFs. For example, the long-range π -conjugation in their 2D planes promotes the delocalization of charge carriers within the network, leading to high mobility and conductivity,^{251,252} as well as providing additional possibility for multifunctional electronic devices for the recently called “MOFtronics.”²⁵³ In particular, 2D c-MOFs can exhibit high

stability together with tunable optoelectronic properties, (photo)-electrochemical activity,^{254,255} ferromagnetic ordering,²⁵⁶ and topological states,²⁵⁷ yielding a potential source for SCs, beyond their use in batteries^{258,259} and supercapacitors.^{260,261} In addition, their liquid-phase processability is particularly relevant for the realization of solution-processed SCs. For example, a thiol-functionalized 2D c-MOF has been recently used as an electron-extracting layer at the perovskite/cathode interface.²⁶² Meanwhile, a Te-based 2D c-MOF was introduced in PSCs to passivate the electron transporting layer (ETL) in TiO_2 , while improving the morphology of the perovskite photoactive film.²⁶³ Despite these promising results, the use of solution-processed 2D c-MOFs in SCs is still in its infancy, even though it is plausible that these materials can prospectively play a significant role in PV devices. In particular, we expect that the progresses in their synthesis, as well as the scaling-up of their synthesis strategies, will be crucial for the rational implementation of 2D c-MOFs in cutting-edge SC technologies.

2.2.3 Two-dimensional carbon nitrides. By attempting to open the zero E_g of graphene to provide intrinsic semiconductivity while maintaining a graphite-like atomic crystalline structure, bottom-up approaches with C-rich and N-rich precursors were successfully reported to produce 2D carbon nitrides (C_xN_y),²⁶⁴ including the most prevalent ones such as graphitic carbon nitride ($\text{g-C}_3\text{N}_4$),^{265,266} C_2N ,^{267–269} C_3N ,^{270,271} and C_5N_2 .²⁷² Owing to their large surface area and tunable optoelectronic properties, such class of materials has been widely investigated for the realization of photocatalysts (and even photocatalyst supports)^{273,274} and (electrochemical) energy storage systems.^{275–277} Beyond these applications, 2D C_xN_y also represents a promising class of solution-processable materials for SCs, as testified by their use in OSCs,^{278,279} DSSCs,^{280–282} and PSCs.^{283–286} However, compared to GRMs, the rational engineering of most 2D C_xN_y materials is still limited, and theoretical studies are needed to elucidate the influence of the number of layers, defects, and chemical modifications on their performance when used as functional components in SCs. Moreover, it should be noted that the precursors used for the synthesis of 2D C_xN_y are often expensive, and the synthesis strategies are complex and require highly controlled experimental conditions. These aspects critically limit their use in massive applications, including SCs. Therefore, the present work will not focus on this class of materials, even though some results achieved with the most established C_xN_y materials are mentioned in the discussion on PV technologies investigated here.

2.3 Classification of semiconductor 2D materials: n-type or p-type materials?

To provide some guidelines regarding their functional role in SCs, semiconductor 2D materials can be classified depending on their (opto)electronic properties. However, for the case of solution-processed 2D materials, such properties are strongly influenced by both structural and chemical characteristics. The possibility to on-demand tune the (opto)electronic properties by structural and chemical engineering is a key feature of solution-processed 2D materials, making them extremely versatile for application in PV devices. As discussed in the following sections



(4, 5, 6, and 7), the structure of SCs is commonly engineered by introducing proper charge transporting layers (CTLs), which efficiently and selectively extract the photogenerated charges, improving the device performances. In this context, it is common to consider p-type and n-type materials to extract holes and electrons, respectively. However, the choice of CTLs can follow more complex rationales. In fact, the charge transporting properties are determined by the entire electronic structure of the materials, as well as by their chemical reactivity with the interfaced materials. As a striking example, MoO_3 , which can also be found in the 2D form, is a typical n-type material that acts as an efficient hole transporting layer (HTL) due to its high ϕ_{W} .^{287,288} The latter can even be higher than 5 eV,²⁸⁹ similar to that exhibited by common p-type materials used to extract photogenerated holes.²⁹⁰ Therefore, MoO_3 can efficiently collect holes from its CB through an electron injection mechanism.²⁹¹ Furthermore, MoO_3 forms a highly p-type-doped interface with active materials having ionization energies lower than ϕ_{W} of MoO_3 , favoring the hole extraction process.^{291–293} Similar to MoO_3 , 2D materials can go against the rules “p-type materials collect holes” and n-type materials collect electrons”; therefore, they should be specifically examined to understand their functional role in the SC structure. Based on this consideration, semiconductor 2D materials will not be classified as n-type or p-type materials because there is no a clear one-to-one correspondence between 2D materials and their electronic properties, as well as between the electronic properties of solution-processed 2D materials and their functional role in PV devices.

2.4 Solution processing of 2D materials

The design, development, and production of (opto)electronic devices^{73,86,294,295} inherently depend on the properties of the available materials.^{83,296} Different methods have been reported for the production and processing of GRMs. The main approaches for the production of GRMs have been summarized in previous works.^{83,296–298} Although proof-of-concept PV devices have been demonstrated for exploiting micromechanically cleaved materials,²⁹⁹ the discovery of scalable methods to produce GRMs with “on-demand” tuned structural and (opto)electronic properties is a “must” for the realization of practical SCs. The production of large-area, high-quality GRMs is still one of the most urgent needs of this research area,^{83,296,297} even though several progresses have been accomplished at the industrial level. The requirement to exercise control at the monolayer level needs the understanding of surface physics and chemistry, which has so far not been fully demonstrated in any multicomponent materials system. For example, progress is being made toward the production of large-area single crystals,^{297,300–306} a key process for the development of high-quality thin films with both optical transparency and electrical conductivity.^{307,308} Growth techniques reported in the literature for 2D materials, e.g., chemical vapor deposition (CVD), molecular beam epitaxy (MBE), and atomic layer deposition (ALD), have been conventionally used to create heterostructures based on graphene, other elemental 2D materials, TMDs, TMOs, h-BN, and oxide materials.⁸³ For example, significant progresses have been

made in the growth of graphene on metals³⁰⁹ and on silicon carbide (SiC).^{83,310,311}

By carefully choosing the individual components, one can tune the growth/production parameters, creating GRMs “on demand” for the design and realization of van der Waals heterostructures with functional properties.^{187,312,313} However, the growth of 2D materials by means of the aforementioned synthesis routes is challenging in the case of nonmetallic substrates.³¹⁴ In order to exploit the availability of high-quality synthetic 2D materials for practical devices, the transfer and alignment processes of 2D films on arbitrary substrates have to be developed. Several transfer processes classified as wet- or dry-transfer have been proposed and utilized so far.^{83,297,305,315–319} In the wet-transfer process, the as-grown 2D material contacts the liquid during at least one step of the process.⁸³ This determines the occurrence of adsorbates that are trapped onto the 2D materials surface, significantly influencing the interface quality. To avoid this drawback, dry-transfer processes have been established to create perfectly clean interfaces.^{83,320} This has been a crucial step for the demonstration of the fundamental properties of 2D materials, which requires extremely low densities of interface traps and dangling bonds.³²¹

Recent reports on the dry transfer of graphene using pick-and-place techniques³²² and exploiting h-BN as the 2D dielectric have successfully achieved extremely high μ (i.e., $350\,000\text{ cm}^2\text{ V}^{-1}\text{ s}^{-1}$) in graphene.³²³ However, transfer processes intrinsically represent limitations for the integration of high-quality 2D materials in practical devices, in which direct material growth on *ad hoc* materials and/or solution-based processing are required for the realization of high-throughput device manufacturing chains. Recently, the direct growth of graphene on glass, creating the so-called “super graphene glass,” has attracted enormous interest to circumvent transfer-process-related issues for practical applications,^{324–327} including transparent conductors, smart windows, simple heating devices, and SC electrodes. However, the CVD growth of high-quality graphene is still challenging, and “super graphene glasses” currently show (opto)electronic properties still far from those of CVD graphene grown on metallic substrates.³²⁴ In fact, on a catalytically inert glass surface, one cannot expect yet to control the graphene growth as done onto a catalytically active metal surface.⁸³

The direct exfoliation of bulk layered crystals by LPE^{328–330} is an industrially relevant strategy for the scalable production and/or processing of GRMs. Herein, we will summarize the main methods for the production and processing of 2D materials in solution, while additional details can be found in recent literature reviews.^{83,205,297,298,331} The LPE process enables the formulation of inks of GRMs in different solvents (Fig. 5a).^{332–335} This is the starting point for the reliable production of devices based on printed technologies,³³³ as well as for targeting the industrial fabrication of GRM-based devices, including SCs (Fig. 5b).²⁰⁵

Liquid phase exfoliation is a versatile technique and it has been established for the exfoliation of numerous layered materials,^{328–330} including graphite, TMDs, TMMs, black phosphorus (BP), and h-BN, just to cite a few. As depicted in Fig. 6, the liquid-phase processing of bulk layered crystals generally



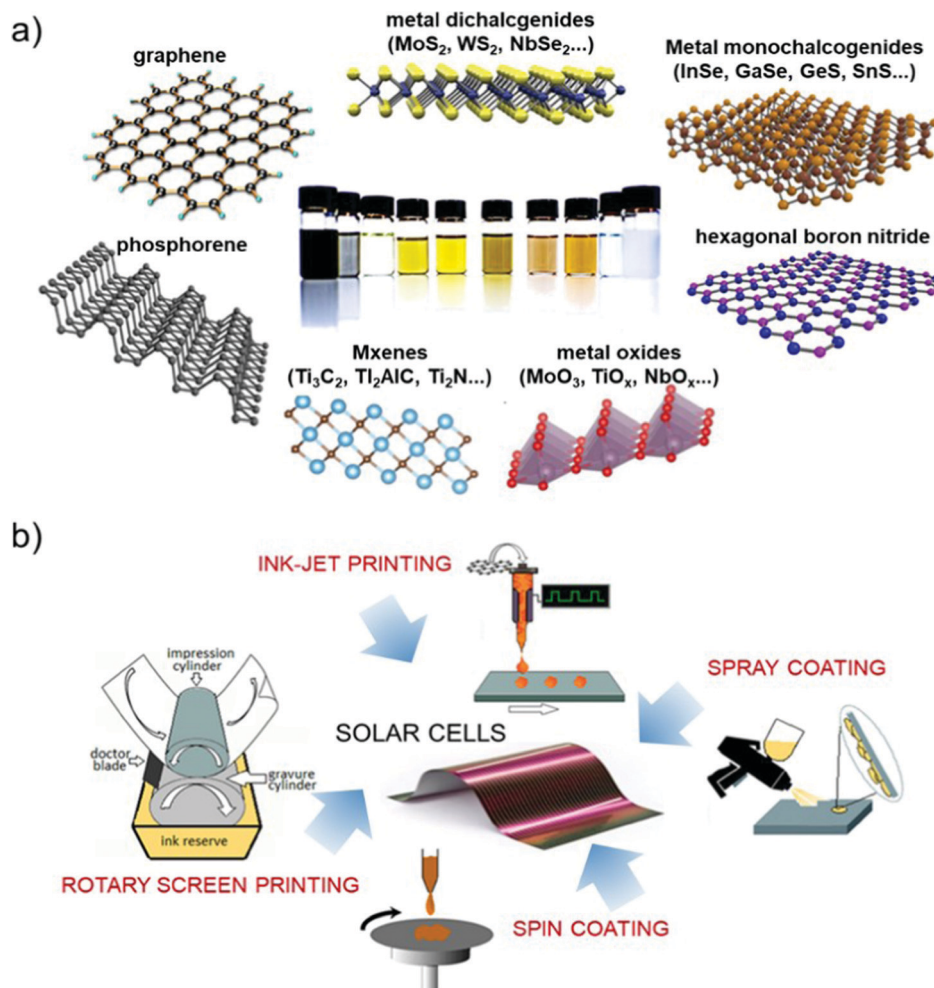


Fig. 5 (a) Schematic of monolayer materials, e.g., graphene, elemental 2D materials (phosphorene), metal dichalcogenides, metal monochalcogenides, MXenes, h-BN, and metal oxides, and their formulation in the form of ink. (b) Schematic of solution-processing methods of SCs, including relevant material deposition techniques (e.g., spin coating, spray coating, inkjet printing, and rotary screen printing).

involves (1) the dispersion of bulk crystals in a solvent; (2) the exfoliation of bulk crystals through (acoustic) cavitation or shear forces (Fig. 6a); (3) the “sorting” (e.g., by ultracentrifugation) of the material flake sizes (Fig. 6b).^{83,205}

In general, the LPE process starts with the dispersion of bulk crystals either in organic solvents³³⁰ or in aqueous solutions, the latter with the aid of surfactants^{329,338,339,340} or polymers.^{341,342} The exfoliation process is commonly carried out by exploiting cavitation^{328–330} or shear forces³⁴³ to produce single- and few-layer materials.³⁴⁴ Ultrasonication-assisted exfoliation of bulk crystals is the prototypical LPE method.^{328,329,345–349}

For the case of graphene, the ultrasonication process produces defect-free flakes (*i.e.*, no additional defects are introduced during exfoliation) as well as achieves concentrations of several grams per liter.³⁵⁰ However, ultrasonication-assisted LPE is not a scalable process, since it is a time-consuming process requiring several hours.²⁰⁵ Other approaches have also been proposed, such as ball milling,^{351–353} shear exfoliation,^{354,355} and microfluidization.^{356–359} All these approaches have pros and cons compared with the ultrasonication method,²⁰⁵ even though some of the apparatus

can yield high-throughput production of 2D materials for industrial applications. Recently, Bonaccorso and co-workers presented a novel approach to exfoliate layered crystals, *i.e.*, graphite, h-BN, and TMDs, based on the high-pressure wet-jet milling (WJM) technique.³⁶⁰ In detail, during the WJM process, a hydraulic piston applies a pressure between 180 and 250 MPa, forcing the solvent/layered-crystal mixture to pass through perforated disks with variable diameters (typically between 0.3 and 0.1 mm), called the nozzle. This process generates shear forces that promote the exfoliation of layered materials.^{359,361} The key advantage of the WJM technique compared to other LPE methods is the small time required to process the sample, which is reduced to less than one second, instead of the several hours required during ultrasonication-assisted exfoliation^{328,329,344–348} or shear exfoliation.^{353,354} By means of the WJM method, a production rate higher than 2 L h^{−1} of 2D crystal dispersion (concentration: 10 g L^{−1}) and an exfoliation yield (defined as the ratio between the weight of the exfoliated material and the weight of initial graphite) of 100% have been demonstrated with a single WJM apparatus.^{359,362} The 2D crystals obtained through



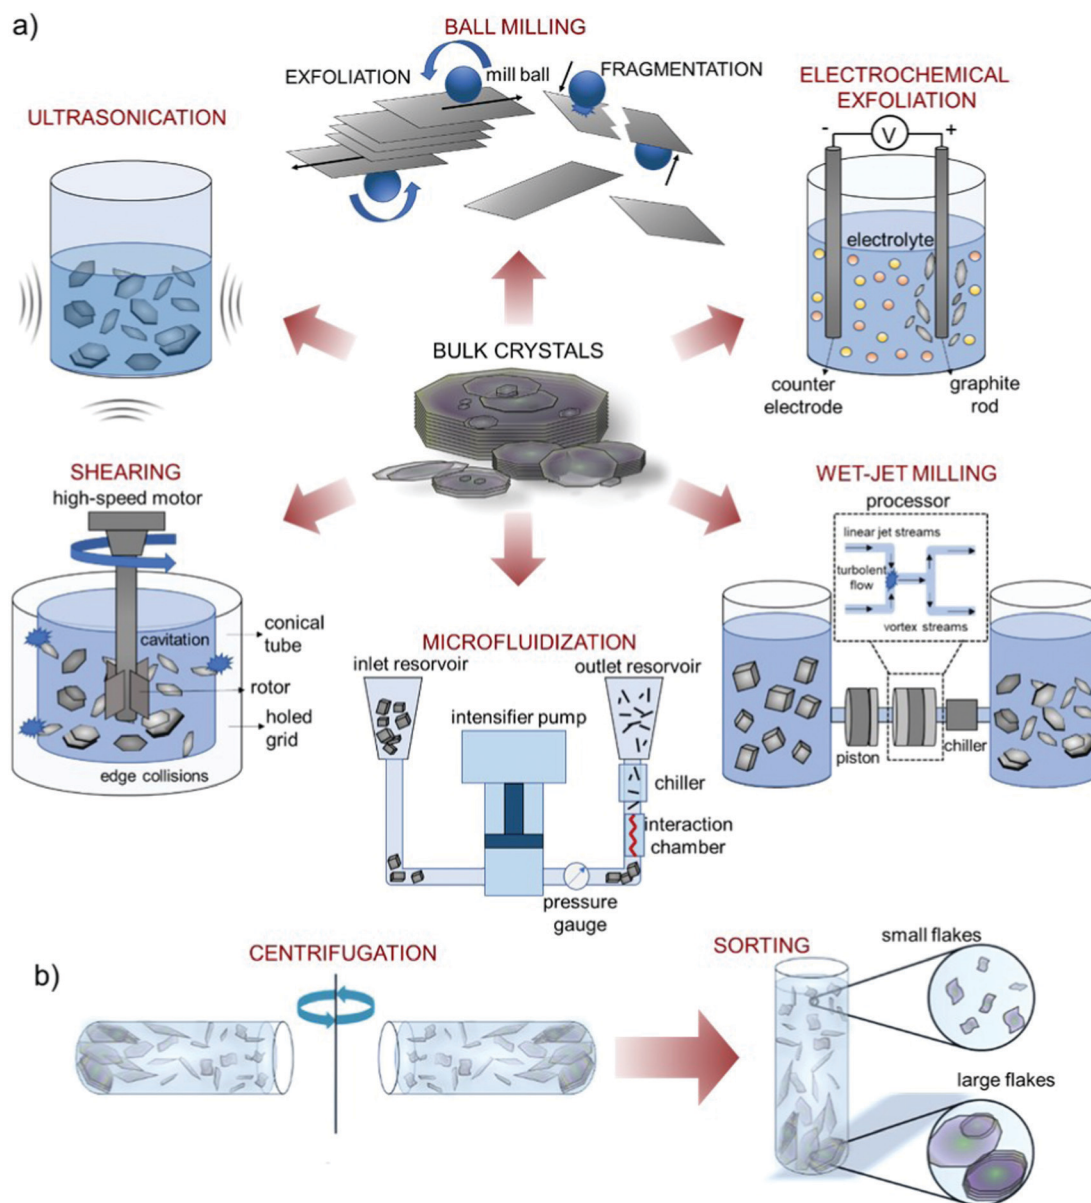


Fig. 6 Schematic of the LPE processes. (a) Schematic of various LPE methods reported in the literature, including ultrasonication, shearing, wet-jet milling, microfluidization, ball milling, and electrochemical exfoliation. Schematic of the LPE methods adapted from ref. 336, 356, 360. (b) Dispersion purification by means of ultracentrifugation (sedimentation-based separation (SBS), and subsequent “sorting” of different material flake sizes. Adapted with permission from ref. 337. Copyright 2017, American Chemical Society.

WJM have already been used for a wide range of ESC applications^{363–371} and composites,³⁷² in which a large volume of material is needed for their industrial implementation. Another approach to upscale the 2D material production (beyond tens of grams per hour) is the electrochemical exfoliation process. In this method, a potential difference is applied between a layered anode/cathode in an electrolyte-containing medium.^{373–375} In these experimental conditions, positive or negative charges can be imparted to the layered materials, promoting the intercalation of oppositely charged ions and facilitating the exfoliation process.^{372–374} These processes can be broadly classified in two classes. The first one is the anodic exfoliation in the

inorganic salts’ aqueous solution, mineral acids, or mixture of water and ionic liquids. The second one is the cathodic exfoliation in organic solvents (e.g., *N*-methyl-2-pyrrolidone, dimethyl sulfoxide, and propylene carbonate) in the presence of alkylammonium salts or Li.³⁷⁴ Electrochemical methods are extremely attractive since they reduce the use of chemical oxidants as the driving force for intercalation or exfoliation, and the electromotive force is controllable for the creation of tunable-material intercalated compound.^{372–374} In addition, the extensive capabilities of the electrochemical exfoliation method to modify materials enables the facile and direct synthesis of functionalized 2D materials with the desired properties for composites,



electronics, and ECS applications.^{372–374} Regardless of the LPE process used to produce 2D materials, a common key issue of the aforementioned methodologies is that the resulting samples are polydisperse in their dimension, typically showing broad distributions of flake thickness and size.^{205,297} Thus, it is crucial to obtain a fine adjustment of the morphological properties by separating small from large flakes³³⁷ and thin from thick ones.³³⁹ This step is typically performed using ultracentrifugation protocols.^{339,376–381} In this context, exfoliated GRMs can be sorted with respect to thickness and lateral size using techniques based on ultracentrifugation in uniform media (SBS)³⁸² or density gradient media (density gradient ultracentrifugation (DGU)).³⁸¹

Another important issue of 2D flakes produced in the form of ink through LPE methods is the re-aggregation of flakes after their deposition/coating. In fact, flake re-aggregation might affect the electronic (*i.e.*, μ , contact resistance) and physical (*i.e.*, roughness) properties of the resulting films. Therefore, suitable strategies must be developed to minimize flake reaggregation with regard to practical applications. For example, the addition of stabilizers (*e.g.*, surfactants and polymers) physically hinders flakes' contact,^{337–339} impeding their aggregation.^{337–339} However, the effect of such stabilizers could affect the electrical performance of the assembled films.^{297,383,384} In addition to the aforementioned issues, some layered materials, such as BP, are unstable under ambient conditions or in the presence of water and/or oxygen.^{385,386} The instability issue, which might be valid for 2D materials either grown by the bottom-up approach (*e.g.*, CVD)^{83,387,388} or produced by micromechanical cleavage,^{69,389,390} can be eliminated by introducing a solvent shell,²⁰⁵ or residual surfactants/polymers adsorbed onto the surface of flakes. Importantly, solvents or surfactant residuals may imply an intrinsic doping of the flakes.²⁰⁵ These effects can be advantageously used to attain controllable doping strategies. The LPE process can also be exploited for the exfoliation of bulk layered materials specifically prepared/synthesized with the desired chemical characteristics (*e.g.*, doping), as for the case of graphite oxide³⁹¹ (*i.e.*, to produce GO).^{83,330} In particular, graphite oxide can be prepared by means of chemical processes that introduce functional groups both at the edges (*e.g.*, COOH and C=O) and on the basal plane (*e.g.*, OH or epoxide groups).^{81,82} The occurrence of these functional groups is fundamental toward the production of GO using well-established methods, including thermal expansion,³⁹² ultrasonication,³⁹³ and stirring³⁹⁴ of graphite oxide. Moreover, the presence of the aforementioned functional groups introduces polarities^{395–397} that facilitate the dispersion of exfoliated graphitic materials in aqueous solutions.^{392,398} Although GO flakes can have lateral sizes up to several microns,³⁹⁹ they exhibit a high density of structural defects,³⁹³ which arise from the chemical treatment disrupting the sp^2 -bonded network.⁸³ Thus, in order to restore both electrical and thermal conductivities of pristine graphene, various strategies have been developed to reduce GO flakes using either chemical³⁹⁷ or physical^{393,397,400} processes. These reduction processes are imperative to produce a sample of the quality approaching that of pristine graphene. Recently, tremendous progresses have been achieved in this direction,

with the demonstration of μ exceeding $1000 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$ in field-effect transistors with microwave-reduced GO.⁴⁰¹

Owing to its scalability and cost-effectiveness, LPE techniques can provide GRMs in massive quantities at an accessible price. Moreover, solution-processed 2D materials can be combined with polymeric materials, while being processed in the form of a coating on different substrates. In this context, progresses have been made on the large-scale placement of 2D material-based inks by means of different deposition/coating systems, such as Langmuir–Blodgett,⁴⁰² spin,^{403–405} spray,^{406–408} and rod⁷³ coating; vacuum filtration,^{409–415} and inkjet,^{332,333,416} gravure,⁴¹⁷ flexographic,⁴¹⁸ and screen⁴¹⁹ printing (including their roll-to-roll (R2R) configurations).⁴²⁰ Advances in this area enabled the layer-by-layer printing of different 2D material-based films, as well as heterostructures and/or heterogeneous structures, on large areas (ranging from the scale of square centimeters to square meters).²⁰⁵ However, beyond uniformity, the roughness of the deposited large-area films is a critical issue, which may degrade the (opto)-electronic properties expected from heterostructures produced through material transfer after micromechanical cleavage or direct growth.¹⁸⁷ However, different from the transfer approach, drop-on-demand printing could meet the large-scale fabrication requirements of practical devices.²⁰⁵ For example, drop-on-demand inkjet printing has been demonstrated for the realization of all-printed, vertically stacked transistors with a graphene source, drain, and gate electrodes; a TMD channel; and an h-BN separator.⁴²¹ The proposed printed device, based on 2D material heterostructures, has shown a μ value of $0.22 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$.⁴²⁰ Despite these important achievements, the obtained μ value is rather low, meaning that further insights are still needed into the assembly of such printed heterostructures.^{187,332} Here, the challenges to be tackled are two-fold: (1) the optimization of ink formulation fulfilling the morphological (*e.g.*, thickness and lateral dimension of the flakes) and rheological (*e.g.*, viscosity and surface tension of the dispersions) property requirements; (2) the optimization of printing parameters for the deposition of uniform 2D material films with high-quality (*i.e.*, clean) interfaces.²⁰⁵ Noteworthy, the surfaces of 2D materials are strongly affected by both solvent and additive (*i.e.*, stabilizers) residuals,²⁰⁵ which, therefore, need to be minimized. Here, a balance must be found between the possibility to have a clean interface and the intrinsic doping (determined by the presence of solvent and additive residuals) on a case-to-case basis, depending on the final application. Overall, notwithstanding the scalable production of GRMs and their film deposition, understanding the precise determination of crystal structures and their crystallographic relationships is of utmost importance for the design and realization of any (opto)electronic device, including PV ones that are discussed here. Further, chemical doping and functionalization are pivotal to properly tune the (opto)electronic properties of the structures.^{344,422–425} Both covalent and noncovalent functionalizations introduce a systematic modification of 2D material properties to control their solubility/processability, the prevention of flake re-aggregation, and their (opto)electronic characteristics (*e.g.*, E_g).^{344,421–423} The chemical modification/functionalization also allows the properties of 2D



materials to be combined with the property portfolio of other compounds.^{344,420} Overall, a thorough understanding of the charge transport and transfer properties, defects (including edge terminations, dopants, point defects, and grain boundaries), environmental contaminants (*e.g.*, surfactants and adsorbates), and chemical reactivity is crucial for the design of practical GRM-based devices.

2.5 Functional roles of solution-processed 2D materials

The understanding of “*how to use 2D materials in SCs*” is not trivial, since their versatility resulting from the immense portfolio of their (tunable) properties can lead to apparently contradictory experimental results. In fact, there exist solution-processed 2D materials that have been applied to collect either photogenerated holes or electrons, while being used as buffer layers to stabilize the interfaces between the materials comprising the SCs, or even as catalysts for the redox reactions involved at the counter electrodes (CEs) in DSSCs, or as electrically conductive materials for current collectors. This aspect is so surprising to the extent that it could even be disappointing, albeit it reveals the easiness to incorporate 2D materials in SC structures to improve their performances. Scheme 1 reports a sketch of the various functional roles of material components in SCs, as they will be detailed for each type of technology in the subsequent sections. Clearly, solution-processed 2D materials have been applied almost everywhere, most of them for more than one functionality. The most representative example material class, namely, “graphene and its derivatives,” has been used for all the functional roles identified here, indicating the importance to specify the structural, morphological, and chemical properties for each material, thereby using a “case-by-case approach.” In addition, this point implicitly stresses the importance of providing a full set of experimental characterizations of 2D materials when used in SCs, so that it is possible to uniquely correlate their functional role to their intrinsic attributes. Even though it is common to refer to electronic structures of 2D materials in ideal stoichiometry to explain their functional role in SCs, it is recommended to provide experimental measurements (beyond those which are used for the characterization of SCs) to confirm the absence of a relevant discrepancy compared to such ideal cases. In fact, defects, surface oxidation, chemical functionalization, and even the simple morphology of 2D materials can result in optoelectronic properties that are completely different from those of their ideally stoichiometric structures. Examples of effective characterizations are absorbance/reflectance measurements coupled with ultraviolet photoelectron spectroscopy and Kelvin probe measurements to provide the first sketch of the energy-band edge positions and WF values of the materials used in the different components of SCs. Possible discrepancies should be explained by investigating the chemistry of the material surface through X-ray photoelectron spectroscopy (XPS). The impact of 2D morphology on the functional role of 2D materials should be supported by proper lateral and thickness analyses through transmission electron microscopy (TEM), atomic force microscopy (AFM), and surface area measurement techniques (*e.g.*, physisorption characterizations), while the structural properties of 2D materials can be rapidly assessed by both Raman

spectroscopy and X-ray diffraction (XRD) characterizations. Electrical and photoelectrical properties, such as (photo)resistivity/(photo)conductivity, of 2D materials could be accessed by realizing and characterizing complementary devices, such as field-effect transistors, as well as a simple four-probe method. These considerations indicate the key importance of providing reliable insights into the nanomaterials, devoted to improve the performance of entire PV systems, which must be carefully rationalized through in-depth experimental characterization. In this context, the efforts recently made to standardize the sequence of methods for characterizing the structural properties of graphene, bilayer graphene, and graphene nanoplatelets in both powder and liquid (*i.e.*, dispersion) forms are noteworthy. The need of such a standard, namely, ISO/TS 21356-1:2021, emerged from the confusion around the terminology of “graphene” used to label commercially available materials. In conjunction with the international ISO/IEC terminology, the ISO/TS 80004-13:2017 standard represents a step forward to the use of (solution-processed) 2D materials with well-defined properties in both laboratory and commercial applications, including SCs.

3. Figures of Merit of Solar Cells

For facilitating comparison, SCs are often ranked in terms of the following FoM:⁵³

(i) EQE, which represents the ratio between the number of charge carriers collected by the cell and that of photon flux (of a given energy) that strikes the cell, *i.e.*,

$$\text{EQE}(\lambda) = \frac{\left(\frac{I}{e}\right)}{\left(\frac{P_{\text{in}}}{hc/\lambda}\right)} \quad (3.1)$$

where I is the electrical current given by the SC, e is the elementary charge ($1.6021766208 \times 10^{-19}$ C), P_{in} is the power of incident light, h is the Planck constant, c is the speed of light in a vacuum, and λ is the photon wavelength.

(ii) Internal quantum efficiency (IQE), *i.e.*, the fraction of absorbed photons converted in I , *i.e.*,

$$\text{IQE}(\lambda) = \frac{\left(\frac{I}{e}\right)}{\left(\frac{P_{\text{in}}}{hc/\lambda}\right) \times (1 - R)} \quad (3.2)$$

(iii) the overall η , defined as the ratio between the maximum output electrical power (P_{max}) of the cell, and P_{in} , *i.e.*,

$$\eta = \frac{P_{\text{max}}}{P_{\text{in}}} = (V_{\text{OC}} \times I_{\text{SC}} \times \text{FF}) \quad (3.3)$$

where V_{OC} is the maximum open-circuit voltage, I_{SC} is the short-circuit current, and FF is the fill factor. Here,

$$\text{FF} = \frac{(V_{\text{MPP}} \times I_{\text{MPP}})}{(V_{\text{OC}} \times I_{\text{SC}})} \quad (3.4)$$



ETLs <ul style="list-style-type: none"> • Graphene & derivatives • Transition metal dichalcogenides (<i>e.g.</i>, MoS₂, TiS₂, SnS₂) • MXenes (<i>e.g.</i>, Ti₃C₂T_x) • Elemental 2D materials (<i>e.g.</i>, black phosphorous/phosphorene) 	HTLs <ul style="list-style-type: none"> • Graphene & derivatives • Transition metal dichalcogenides (<i>e.g.</i>, MoS₂, MoSe₂, WS₂, WSe₂, TaS₂, NbSe₂) • Group-15 metal chalcogenides (<i>e.g.</i>, Bi₂Se₃) • MXenes (<i>e.g.</i>, Ti₃C₂T_x) • III-VI compounds (<i>e.g.</i>, In₂Se₃) • Elemental 2D materials (<i>e.g.</i>, black phosphorous) 	Dopants for CTLs <ul style="list-style-type: none"> • Graphene & derivatives • Transition metal dichalcogenides (<i>e.g.</i>, MoS₂, WS₂) • Elemental 2D materials (<i>e.g.</i>, black phosphorous, Antimonene) • g-C₃N₄ • Group-15 metal chalcogenides (<i>e.g.</i>, Bi₂Te₃)
Electrodes (current collector) <ul style="list-style-type: none"> • Graphene & derivatives • MXenes (<i>e.g.</i>, Ti₃C₂T_x) 	Catalysts for CE (in DSSCs) <ul style="list-style-type: none"> • Graphene & derivatives • Transition metal dichalcogenides (<i>e.g.</i>, MoS₂, WS₂, WSe₂, NbSe₂, NiS₂, NiSe₂, TiS₂ and TaSe₂) • Group-15 metal chalcogenides (<i>e.g.</i>, Bi₂Se₃) 	Additives for photoactives <ul style="list-style-type: none"> • Graphene & derivatives • Transition metal dichalcogenides (<i>e.g.</i>, WSe₂) • Elemental 2D materials (<i>e.g.</i>, black phosphorous/phosphorene) • MXenes (<i>e.g.</i>, Ti₃C₂T_x) • Metal oxysulfides (<i>e.g.</i>, Bi₂OS₂) • MOFs • 2D perovskites (<i>e.g.</i>, (PEA)₂PbI₄) • g-C₃N₄
Buffer layers (protective layers and passivating layers) <ul style="list-style-type: none"> • Graphene & derivatives • Transition metal dichalcogenides (<i>e.g.</i>, MoS₂ and TiS₂) • Elemental 2D materials (<i>e.g.</i>, black phosphorous) • Group-15 metal chalcogenides (<i>e.g.</i>, Bi₂Te₃) • g-C₃N₄ • 2D c-MOFs • 2D perovskites 	Interconnecting layers <ul style="list-style-type: none"> • Graphene & derivatives • Transition metal dichalcogenides (<i>e.g.</i>, MoS₂) 	Encapsulants <ul style="list-style-type: none"> • h-BN

Scheme 1 Functional components of SCs and the corresponding 2D materials reported in the literature for such a role. The 2D materials listed here correspond to those reported in the subsequent sections for each type of SC technology reviewed in this work.

where V_{MPP} and I_{MPP} are the voltage and current, respectively, at the maximum power point (MPPT), defined as the voltage at which $d(IV)/dV = 0$.

Since the application of solution-processed GRMs as transparent conductive electrode (TCEs) for SCs will be examined

here, the FoM determining the quality of TCEs are also reported and discussed. The quality of TCEs is mainly assessed through two crucial parameters: R_s and T_r , which should be $< 10 \Omega \square^{-1}$ and $> 90\%$, respectively.⁷³ Moreover, a trade-off between R_s and T_r is unavoidable for TCEs.



To evaluate TCEs, the following semiempirical FoM has been proposed:⁴²⁶

$$\Phi_H = \frac{T_r^x}{R_s} \quad (3.5)$$

where exponent x determines the required T_r value for a specific purpose.

Notably, R_s depends on both charge carrier density (N_d) and μ ($\text{cm}^2 \text{V}^{-1} \text{s}^{-1}$),⁴²⁷ as expressed by the following equation:

$$R_s = \frac{1}{\mu N_d t} \quad (3.6)$$

where t is the thickness of the TCE film.

In order to describe the frequency dependence of the T_r losses in TCEs,^{428–430} as well as the critical reflection at the air/film/substrate interfaces,⁴³¹ the following equation for T_r has been proposed (for thickness $\ll \lambda/2 \cdot \pi \cdot n_{\text{film}}$, where n_{film} is the refractive index of the film):

$$T_r(\lambda) = \frac{16n_{\text{sub}}^2}{R_s(1+n_{\text{sub}})^4} \times \frac{1}{\left(1 + \frac{Z_0}{R_s} \times \frac{1}{(1+n_{\text{sub}})} \times \frac{\sigma_{\text{opt}}}{\sigma_{\text{dc}}}\right)} \quad (3.7)$$

In eqn (3.7), Z_0 is the vacuum impedance (377 Ω);⁴²⁷ σ_{opt} and σ_{dc} are the optical and electrical dc conductivities (also simply referred to as σ) of the material, respectively; and n_{sub} is the refractive index of the substrate. In eqn (3.5), the relationship between T_r and R_s strongly depends on the ratio $\sigma_{\text{dc}}/\sigma_{\text{opt}}$, which can be used as another FoM.⁴³² A high value of $\sigma_{\text{dc}}/\sigma_{\text{opt}}$ implies high T_r (> 90%) and low R_s (< 10 $\Omega \square^{-1}$), which are the desired properties for a TCE.⁷³ In order to achieve commercial TCE performance ($R_s \leq 100 \Omega \square^{-1}$ and $T_r \geq 90\%$ in the visible frequency range), an ideal value of $\sigma_{\text{dc}}/\sigma_{\text{opt}} \geq 35$ is typically required. It is noteworthy that α in the visible spectrum (α_{vis}) arises from the tail of the free-carrier absorption, as described by Drude's theory⁴³³ and is determined by

$$\alpha_{\text{vis}} = \frac{e^3}{4\pi^2 \epsilon_0 c^3} \frac{N_d \lambda^2}{\sqrt{\epsilon_{\infty}} \mu m_{\text{eff}}^2} \quad (3.8)$$

The latter equation shows the direct proportionality between α_{vis} and N_d/μ . This evidences that α_{vis} can be reduced by decreasing N_d and increasing μ , showing a strategy commonly adopted to design effective TCEs.

In addition to R_s and T_r , environmental stability and abrasion resistance are also decisive factors to select TCE materials.

For the specific case of DSSCs, for example, the transport of charge carriers from the photoanode to CE is hindered by several resistances.^{434–437} The latter include the series resistance comprising R_s of TCE and contact resistance of the cell; the transport resistance of electrons in the TiO_2 film (R_{TiO_2}); the resistance at the TCO/ TiO_2 contact ($R_{\text{TCO-TiO}_2}$); the charge transfer resistance of charge recombination between the electrons in the TiO_2 film and ions in the electrolyte (R_{rec}); the charge transfer resistance at the CE/electrolyte interface (R_{CT}); the charge transfer resistance at the exposed TCO/electrolyte interface ($R_{\text{TCO-electr.}}$); and the Warburg parameter, which describes the Nernst diffusion of active ions in the electrolyte (Z_d).

Typically, R_{CT} is often dominant among multiple charge transfer resistances. However, in large-area DSSCs, R_s also significantly determines FF losses.⁴³⁸ The smaller the R_s , the higher is the FF, resulting in higher η .^{439–441} Concerning the electrocatalytic activity of CE, R_{CT} can be explained in terms of current density (J), as expressed by the following equation:

$$R_{\text{CT}} = \frac{RT}{nFJ} \quad (3.9)$$

where R , T , n , and F are the gas constant, temperature, number of electrons transferred in the elementary electrode reaction ($n = 2$), and Faraday constant, respectively.⁴⁴²

4. OSCs

OSCs hold remarkable potential for low-cost, flexible PVs, presenting both compatibility with R2R large-area fabrication^{443–445} and impressive short-energy pay-back times.⁴⁴⁶ Bulk-heterojunction (BHJ) OSCs, exploiting blends of p-type polymer (or organic small-molecule) donor/n-type fullerene (or other kind of organic small-molecule) acceptor materials dissolved in a common solvent, have opened an avenue for promising research activity to improve the η value of SCs,⁴⁴⁷ as well as the overall performance of photoelectrochemical cells.^{448–455} The BHJ configuration maximizes the donor/acceptor interfacial area, facilitating exciton dissociation and charge transfer by forming a bicontinuous interpenetrated charge transport network in the photoactive layer.^{456,457} In addition, the incorporation of layers with hole and electron transporting (or blocking) properties between the donor/acceptor active layer and anode/cathode promotes and balances the extraction/collection of photogenerated charges.⁴⁵⁸ All these properties make the BHJ concept a landmark in OSC development, as well as a plethora of other applications (*e.g.*, photodetectors⁴⁵⁹ and biosensing devices^{460–462}). Historically, the development of low-bandgap polymers, interfacial engineering, and fabrication techniques allowed BHJ to achieve η exceeding 9% for single-junction cells^{463–467} and 10% for tandem cells.⁴⁶⁸ More recently, non-fullerene acceptors (NFAs) have dominated the OSC field due to significant performance and stability improvements.⁴⁶⁹ Compared with their fullerene-based counterparts, NFAs exhibit tunable bandgaps that extend their light absorption in the NIR region.⁴⁶⁸ In addition, their tunable energy levels can adjust the energy-level alignments between the constituent layers in OSCs to minimize the energy offsets, increasing the V_{OC} .⁴⁶⁸ Lastly, their crystallinity can be easily tuned to finely control the photoactive-layer morphology, improving the device stability.^{470–472} Nowadays, state-of-the-art OSCs exhibit η values over 17% for both single-junction cells and two-terminal tandem cells, mainly due to the rapid developments of NFAs, as well as advanced device engineering.^{473–477} In particular, the combination of low-bandgap donors and NFA-enabled OSCs has resulted in the achievement of record efficiency of 18.3%.⁴⁷⁸

In a typical OSC structure, GRMs can be incorporated either as additional components or to replace traditional materials, aiming at both performance and stability enhancement. In this context,





Fig. 7 Two-dimensional materials used as OSC components, including electrodes, CTLs/buffer layers, and photoactive layers. RGO and electrochemically exfoliated graphene have been used as the TCEs. Functionalized graphene molecules, GO, and TMDs such as MoS_2 and WS_2 have been investigated as HTLs. Graphene-based molecules, WSe_2 , and MoSe_2 have been used as electron acceptors in binary blends or additives in ternary OSCs. Lastly, OSCs including functionalized graphene or BP as ETLs or interlayers have also been reported.

GRMs have been used to fulfil several functions (Fig. 7) such as (a) transparent front electrode (*i.e.*, TCE)^{479–481} or back electrode,^{482–484} (b) electron acceptors in binary OSCs or additives in ternary OSCs in the form of nanoflakes dispersed in donor-acceptor matrices;^{336,485–487} (c) ϕ_W -tuned HTLs/ETLs^{488–490} or interfacial layers in tandem OSCs.^{491–493} In the following subsections, the application of solution-processed GRMs into OSC structures will be examined for each functional device component.

4.1. TCEs

Graphene has been largely investigated as the TCE in OSCs to replace traditional ITO electrodes. Actually, ITO is currently the most established TCE material for rigid OSCs due to its excellent conductivity (*i.e.*, $R_s < 10 \, \Omega \, \square^{-1}$ for 100 nm-thick films)⁴⁹⁵ and high T_r ($> 80\%$) in the visible spectrum. However, some drawbacks, including the scarcity of In, expensiveness of the sputter deposition processes, and its polycrystalline structure, makes the ITO films brittle when they are repeatedly bent or stretched,⁴⁹⁶ nullifying their use in flexible OSCs. In addition, it is recognized that ITO elements diffuse through the photoactive layer, leading to a significant decrease in the OSC performance.^{497–499} Alternative TCEs based on CNTs,^{500,501} metallic nanowires,⁵⁰² and conductive polymers⁵⁰³ have been proposed and used in OSCs.

However, these TCEs exhibit high surface roughness and/or large R_s , which reduce the reproducibility rate of the devices.^{499–502}

Alternatively, TCEs based on graphene rapidly emerged, and several approaches have been implemented to decrease the R_s values of graphene-based TCEs toward commercially competitive values.⁷³ For example, Wang *et al.* reported poly(3-hexylthiophene):[6,6]-phenyl C61-butyric acid methyl ester (P3HT:PC₆₁BM)-based OSCs incorporating a TCE comprising 4-layer HNO_3 -doped graphene prepared by a layer-by-layer transfer method.⁵⁰⁴ An η value of 2.5% was obtained by the additional evaporation of a thin layer of MoO_3 over the TCE in order to improve its hydrophilicity and to tune its ϕ_W from 4.36 to 5.37 eV.⁵⁰³ Currently, the highest η values of 6.1% and 7.1% reported for flexible conventional and inverted OSCs, respectively, have been achieved using graphene-based TCEs produced through the CVD method.⁵⁰⁵ Notably, these results have been achieved by applying a MoO_3 buffer layer onto graphene-based TCEs.⁵⁰⁴ More recently, η as high as 8.48% has been achieved in tandem OSCs, which combine a wide-bandgap small molecule with low-bandgap polymer using Au-doped single-layer graphene nanoribbons (GNRs) as the TCE.⁵⁰⁶ Although the CVD is an efficient approach to produce effective graphene-based TCEs,^{507–509} the transfer process of the as-grown graphene films onto a target substrate is still critical, negatively impacting the manufacturing time and cost. In this regard, the chemical



exfoliation of GO through ultrasonication or rapid thermal expansion, followed by reduction with chemical⁵¹⁰ or photo-assisted routes,⁵¹¹ is a reliable low-cost top-down alternative approach, compatible with R2R mass production.⁸³ As discussed in Section 2, RGO can be easily produced in bulk quantities in the form of ink, taking advantage of its solubility in common solvents,⁵¹² including water. Consequently, there has been an extensive research effort on the use of RGO as TCE in OSCs.^{513–515} Flexible OSCs based on a RGO film as the TCE were firstly fabricated using P3HT:PC₆₁BM.⁵¹⁴ The RGO TCE was produced by spin coating GO flakes over a rigid SiO₂/Si substrate. The resulting GO film was then reduced by thermal annealing and transferred onto a polyethylene terephthalate (PET) substrate, yielding the RGO TCE. However, the constructed devices (area: 1 mm²) have shown a low η value ($\sim 0.78\%$), which was attributed to the low T_r (65%) and high R_s of the RGO films ($\sim 3.2 \text{ k}\Omega \square^{-1}$) compared with those of the ITO reference (90% and $15 \Omega \square^{-1}$, respectively).

Geng *et al.*⁵¹⁶ realized graphene-based TCEs using chemically converted graphene (CCG). This was produced by the chemical reduction of GO produced in the form of dispersion without the need of dispersants.⁵¹⁵ The reduction was accomplished by annealing GO under a vacuum in a furnace tube. This treatment resulted in the recovery of the sp²-carbon networks of the graphene sheets. The CCG films exhibited $R_s = 103 \Omega \square^{-1}$ and $T_r = 50\%$. The P3HT:PC₆₁BM-based OSC with CCG-based TCE yielded an η value of 1.01%, which was approximately half that reached by the reference OSC based on ITO.

In the same framework, an efficient reduction method based on laser illumination was demonstrated by Kymakis *et al.*⁵¹⁷ for the fabrication of flexible graphene-based TCEs, which can be spin cast on substrates that are sensitive to temperature. Femtosecond laser-treated RGO (LRGO) films exhibited T_r of 70% and R_s of $1.6 \text{ k}\Omega \square^{-1}$ and were subsequently incorporated as the TCE in P3HT:PC₆₁BM-based OSCs, yielding an η value of $\sim 1.1\%$.⁵¹⁶ Additionally, the as-produced graphene-based OSCs were bent to angles up to 135° without η deterioration, which is different from ITO-based OSCs that failed completely at bending angles greater than 65°.^{518,519}

In order to improve the trade-off between T_r and R_s , the use of a mesh structure with periodic lines, as exploited for Cu-based⁵²⁰ and Si-based⁵²¹ electrodes appeared to be an eye-catching strategy even for graphene-based TCEs. Following this strategy, R_s and T_r of TCEs can be controlled by varying the grid width, spacing, and thickness of the mesh structure.⁵²² Konios *et al.*⁵²³ demonstrated a scalable one-step patterning of RGO films on PET or glass substrates based on femtosecond laser irradiation treatments. The authors proved an accurate control of RGO micro-mesh (RGOMM) features on both rigid (glass) and flexible (PET) substrates.⁵²² In particular, they obtained a RGO electrode with T_r varying from $\sim 20\%$ to $\sim 85\%$ without deteriorating R_s .⁵²² The as-produced RGOMM was then used as TCE in small- and large-area OSCs based on poly[N-9'-heptadecan-2,7-carbazole-*alt*-5,5-(4',7'-di-2-thienyl-2',1',3'-benzothiadiazole)]-[6,6]-phenyl-C71-butyric acid methyl ester (PCDTBT:PC₇₁BM), achieving an η value of 3.67% and 3.05% on glass and flexible substrates, respectively.⁵²²

More recently, electrochemically exfoliated graphene (e-graphene) was used as an alternative to RGO for TCE, avoiding the need for the harsh conditions necessary for the graphite oxidation step.⁵²⁴ TCEs based on e-graphene were then formed by spray coating e-graphene dispersion.⁵²³ The as-produced films exhibited R_s between $520 \Omega \square^{-1}$ (at T_r of 70%) and $180 \Omega \square^{-1}$ (at T_r of 55%).⁵²⁵ The as-produced TCEs were used in a thieno[3,4-*b*]-thiophene/benzodithiophene:phenyl-C71-butyric acid methyl ester (PTB7:PCB₇₁M)-based OSCs, which reached an η value of 4.23%.⁵²³ Subsequently, a mixed-dimensional TCE using silver nanowires (AgNWs) and e-graphene was also demonstrated, achieving an η value of 6.57%.⁵²⁵ The addition of e-graphene on the AgNW network led to a decrease in R_s from 78 to $13.7 \Omega \square^{-1}$ and a reduction in film roughness from 16.4 to 4.6 nm.⁵²⁶

Recently, a graphene-based TCE prepared by stacking polyimide on graphene led to an ultraclean graphene surface, allowing the flexible device to reach a record high η value of 15.2% for flexible OSCs.⁵²⁷ Alternative to the use of high-quality graphene, benzimidazole-doped graphene was also proposed to achieve a trade-off between T_r and R_s , enabling the realization of flexible OSC based on a 3-layer benzimidazole-doped graphene-based anode, with an η value of 6.85%.⁵²⁸

Lastly, both coupling of graphene with metallic grids^{529,530} and graphene/metal hybridization^{531–534} are currently prevalent strategies used to achieve an optimal balance between T_r ($>90\%$) and R_s ($<100 \Omega \square^{-1}$). Table 1 summarizes the main experimental results achieved with OSCs using graphene-based TCEs.

4.2 Active layer components

Electron acceptors. The photoactive layer of an OSC typically comprises a bicontinuous interpenetrating network of electron donor and acceptor materials at the nanometer scale, which is referred to as the BHJ.^{535–538} Traditionally, electron donors are mainly based on conjugated polymers,^{539–541} while typical electron acceptors are fullerene derivatives.^{534–537,542} Although fullerenes exhibit high electron μ (μ_e) and high exciton diffusion length,⁵⁴³ their low light absorption within the solar spectrum restricts the maximum attainable V_{OC} in OSCs.^{544–548} Therefore, alternative acceptors based on both graphene derivatives^{549–552} and small molecules^{553–559} have been successfully proposed to provide an “on-demand” tuning of the LUMO level. Among the 2D materials, functionalized GO and graphene QDs (GQDs) have been largely investigated as solution-processed electron acceptors in OSCs.^{560–562} Liu *et al.*⁵⁶³ functionalized GO with phenyl isocyanate to be used as an electron acceptor in OSCs. The resulting OSCs based on poly(3-octylthiophene-2,5-diyl) (P3OT) as the polymer donor exhibited an η value of 1.4%.⁵⁶² Functionalized GO was also blended with P3HT, achieving an η value of $\sim 1.1\%$.⁵⁴⁸ When P3HT was blended with GQDs functionalized with aniline (ANIGQDs), the resulting OSCs reached an η value of $\sim 1.14\%$.⁵⁶⁴

By a simple lithiation synthesis, Yu *et al.*⁵⁶⁵ covalently joined C₆₀ onto a GO surface. Thus, they obtained a GO:C₆₀ hybrid that was used as an electron acceptor in P3HT-based OSCs, providing an η value of 1.22% (2.5 times higher than the η value measured



Table 1 Summary of the PV performance of OSCs using graphene-based TCEs

Material	Usage	Device structure	Cell performance				Ref.
			J_{sc} (mA cm ⁻²)	V_{OC} (V)	FF(–)	η (%)	
Chemical and thermal RGO	TCE	PET/RGO/PEDOT:PSS/P3HT:PC ₆₁ BM/LiF/Al	1.18	0.46	0.24	0.13	512
Chemical and thermal RGO	TCE	Glass/RGO/PEDOT:PSS/P3HT:PC ₆₁ BM/Al	1.84	0.44	0.25	0.2	513
Chemical RGO	TCE	PET/RGO/PEDOT:PSS/P3HT:PC ₆₁ BM/TiO ₂ /Al	4.39	0.56	0.32	0.78	514
Laser RGO (LRGO)	TCE	PET/LRGO/PEDOT:PSS/P3HT:PC ₆₁ BM/Al	5.62	0.57	0.34	1.1	516
RGO micromesh (RGOMM)	TCE	PET/RGOMMs/PEDOT:PSS/PCDTBT:PC ₇₁ BM/TiO _x /Al	7.81	0.85	0.46	3.05	522
Electrochemical exfoliated graphene (EG)	TCE	PEN/EG/PEDOT:PSS/PTB7:PC ₆₁ BM/Ba/Al	9.97	0.71	0.59	4.23	524
EG-AgNWs	TCE	PEN/EG-AgNWs/PEDOT:PSS/PTB7:PC ₇₁ BM/Ba/Al	15.5	0.73	0.58	6.57	525
PEDOT-doped graphene	TCE	PEDOT-doped graphene/PEDOT:PSS/P3HT:PC ₆₀ BM/bathocuproine (BCP)/Al	9.07	0.55	0.49	2.45	494
PEDOT-doped graphene	TCE	PEDOT-doped graphene/PEDOT:PSS/PBDTTT-C-T:PC ₇₀ BM/BCP/Al	14.57	0.70	0.45	4.64	493
Polyimide/graphene	TCE	Polyimide/graphene/PEDOT:PSS/PM6:Y6/PDINO/Al	25.8	0.84	0.70	15.2	526
Cu/graphene hybrid	TCE	Graphene/Cu/PEIE ⁺ Blm ₄ [–] /PC ₇₁ BM:PTB7/MoO ₃ /Ag	13.01	0.73	0.46	4.38	530
Cu/graphene hybrid	TCE	Graphene/Cu/PEDOT:PSS/PTB7:PC ₇₁ BM/PEIE ⁺ Blm ₄ [–] /aL	12.99	0.58	0.42	3.16	530
Ag grid/graphene	TCE	Ag grid/graphene/PEDOT:PSS/P3HT:PCBM/Ca/Al	7.64	0.57	0.58	2.55	528
Graphene quantum dots (GQDs)-mixed Ag nanowires (NWs)/graphene	TCE	GQDs-mixed Ag NWs/graphene/PEDOT:PSS/P3HT:PCBM/Al	10.43	0.59	0.59	3.66	531
Ag NWs/GO	TCE	Ag NWs/GO/PEDOT:PSS/P3HT:PC ₇₀ BM/LiF/Al	9.53	0.59	0.57	3.26	532
Ag NWs/GO	TCE	Ag NWs/GO/PEDOT:PSS/ptb7:PC ₇₀ BM/LiF/Al	19.84	0.68	0.57	7.62	532
Graphene:Ag NWs composite	TCE	Graphene:Ag NWs/PH1000/PEDOT:PSS/PM6:Y6/pdino/Al	23.2	0.83	0.70	13.44	533

for GO-free device ($\eta = 0.47\%$). This performance enhancement was attributed to the optimal percolation networks for electron transport through the GO flakes.

Stylianakis *et al.*⁵⁶⁶ functionalized GO flakes by linking them *via* peptide bonds to acylated groups (GO-COCl), as well as to 3,5-dinitrobenzoyl chloride with the amino groups of ethylenediamine (GO-EDNB). The resulting GO-EDNB was used as an electron acceptor material in P3HT-based OSCs, which achieved an η value of 0.96%.⁵⁶⁵ However, it is noteworthy that the LUMO level of GO-EDNB was 3.4 eV, which means that it is able to provide an energetic offset for exciton dissociation only with P3HT (LUMO_{P3HT} = 3 eV).⁵⁶⁵ This condition, which is not met by the state-of-the-art polymer donors, prevents the use of GO-EDNB as a universal electron acceptor.⁵⁶⁵ These results evinced the need of exploring alternative functionalization routes for graphene derivatives to improve the distribution of flakes in the polymer matrix, while tuning their electronic structure (*i.e.*, achieving an ideal energy offset between the LUMO levels of the polymers and graphene derivatives). Based on this consideration, a photochemical functionalization of GO through laser-induced covalent grafting of GO nanosheets with EDNB molecules (LGO-EDNB) was subsequently demonstrated to tune the GO energy levels.⁵⁶⁷ The as-produced LGO-EDNB has shown excellent processability in organic solvents commonly used for prototypical polymer donors.⁵⁶⁶ The HOMO/LUMO levels of LGO-EDNB were tuned by adjusting the laser irradiation parameters.⁵⁶⁶ The optimized LGO-EDNB displayed an E_g value of 1.7 eV and LUMO level of 4.1 eV. Thus, it was used as an electron acceptor in PCDTBT-based OSCs, achieving a V_{OC} value of 1.17 V and an η value of 2.41%.⁵⁶⁶

Pristine RGO sheets were also incorporated in the nano-architecture of TiO₂ nanorod (NR)-ZnO NP/P3HT hybrid OSCs,⁵⁶⁸ and η of $\sim 3.8\%$ was achieved for a 900 nm-thick TiO₂ NR array. According to the authors, the RGO behaves as an energy-matched auxiliary electron acceptor in the hybrid

structure, connecting the electron transport pathways provided by the 3D ZnO network and TiO₂ NR array to the fluorine-doped tin oxide (FTO) substrate.⁵⁶⁷ In addition, it was concluded that the incorporation of RGO with low C-to-O atomic ratio stabilizes the active layer infiltrated in the interstices of the TiO₂ NR array.⁵⁶⁷

Beyond more conventional 2D materials, 2D-conjugated polymers have been commonly proposed as potential donor materials for high-performance OSCs. In particular, 2D-conjugated polymers based on bithienylbenzodithiophene-*alt*-benzotriazole backbone bearing different conjugated side chains, commonly named J-series polymers, enabled the realization of OSCs with η approaching values obtained from state-of-the-art materials.⁵⁶⁹

Additives in ternary OSCs. An effective way to enhance the performance of BHJ OSCs relies on the addition of a third component into the polymer–fullerene binary blend, generating a ternary OSC.⁵⁷⁰

In principle, the ternary structure can address most of the deficiencies of the BHJ binary blend. In particular, the absorption spectral window of the polymer donor can be extended and the exciton dissociation and charge transport can be enhanced owing to the introduction of additional interfaces, and the morphological properties of the photoactive layer can also be tuned for favorable cell operation. However, it is crucial that the LUMO and HOMO levels of the additive component must lie between the LUMO and HOMO levels of fullerene and the polymer, respectively, so that suitable energy offsets are present at the material interfaces. In this regard, indene-C₆₀ bisadduct (ICBA), whose energy levels lie between the polymer donor and fullerene acceptor, has been successfully used as the third component in ternary blends.⁵⁷¹ As an alternative to ICBA, solution-processed graphene derivatives can be ideal additives in ternary OSCs, since a remarkable μ value in the device is expected to be achieved *via* graphene addition. In addition, graphene plays a relevant role in charge transfer processes,⁵⁷² increasing the exciton separation efficiency. Consequently, pristine



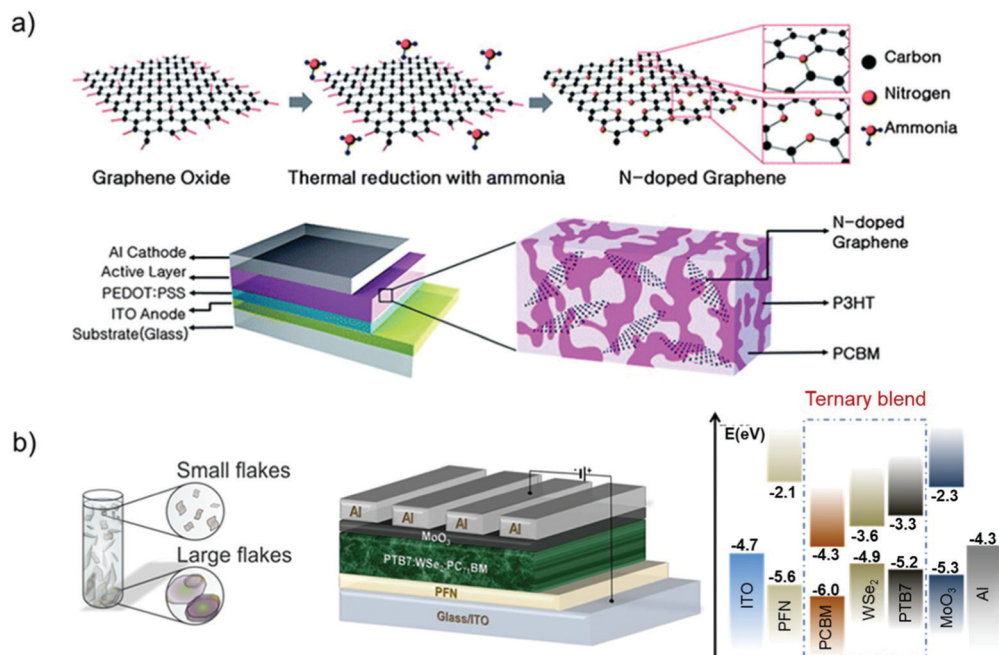


Fig. 8 (a) Schematic of the N-doping process of RGO and BHJ OSC using N-doped graphene/P3HT:PC₆₁BM as the active layer. Adapted from ref. 572. (b) Schematic of the WSe₂ flake production through LPE, and schematic of the device structure and energy levels. Adapted with permission from ref. 336, Copyright 2017, American Chemical Society.

graphene flakes and RGO have been investigated as additives in ternary OSCs to increase their PV performance. For example, Jun *et al.*⁵⁷³ used RGO flakes n-doped with N (NRGO) as the additive material in P3HT:PC₆₁BM-based OSCs, which exhibited a ~40% increase in η (4.39%) compared to that of a binary OSC. The beneficial effect of NRGO addition was associated to the enhancement of μ_e in the photoactive layer (from 3.1×10^{-7} to $5.4 \times 10^{-7} \text{ m}^2 \text{ V}^{-1} \text{ s}^{-1}$) (Fig. 8a). However, because of the absence of an appropriate bandgap, the flakes act as carrier traps in the BHJ. Therefore, NRGO was not an energy cascade material, but it only provided additional charge transport pathways.

Similarly, Robaey *et al.*⁵⁷⁴ used solution-processed graphene flakes, produced by the LPE of pristine graphite, as an additive in P3HT:PC₆₁BM-based OSCs. It was shown that graphene addition determines the formation of a continuous active film with an interpenetrating structure by improving the crystallinity of P3HT. Nevertheless, like NRGO, solution-processed graphene flakes cannot be considered as an energy cascade component in a ternary BHJ OSC due to lack of a bandgap and therefore appropriate energy level matching. Contrarily, solution-processed graphene flakes can be considered as an additive to improve the crystallization and morphology of P3HT, beyond the improvement of charge transport properties. Consequently, graphene flakes can favor better balancing between μ_e and μ_h compared to the reference cell.

Graphene nanoflakes with controlled lateral size and functionalized with EDNB (EDNB-GNFs) were demonstrated as a ternary compound acting as an efficient electron-cascade acceptor material in air-processed PCDTBT:PC₇₁BM-based OSCs.⁴⁸⁴ The functionalization process allowed the HOMO and LUMO levels of GNFs to be matched with the HOMO and LUMO levels of the

hosting polymer and fullerene components, respectively. Furthermore, EDNB-GNFs acted as a highly conductive bridge between polymer chains and fullerene balls, thus offering two additional interfaces for exciton dissociation, as well as multiple routes for charge transfer at the donor/acceptor interfaces. The as-prepared ternary OSCs achieved an η value of 6.59%, which was ~18% higher than that of the binary reference ($\eta = 5.59\%$). The same group investigated the role of GO covalently linked with porphyrin moieties (GO-TPP) into the active layer of PCDTBT:PC₇₁BM and PTB7:PC₇₁BM,⁵⁷⁵ showing that the addition of GO-TPP induces favorable energy alignment between the energy levels of the donor and acceptor, facilitating the electron-cascade effect. The optimized ternary PTB7-based OSCs, containing 0.3% GO-TPP, exhibited a remarkable η of 8.81%, which was ~16% higher than the binary reference one.⁵⁷⁴

Kim *et al.*⁵⁷⁶ incorporated GO-QDs in PTB7:PC₇₁BM-based OSCs and investigated the effect of reduction of GO on the PV performance. It was found that the addition of partially reduced GO-QDs (RGO-QDs) in the active layer enhanced the η value from 6.7% up to 7.6% because of the ideal balance between optical absorption and conductivity of QDs.⁵⁷⁵ Most recently, RGO-Sb₂S₃ hybrid flakes have been used as additives in PCDTBT:PC₇₁BM-based OSCs.⁵⁷⁷ Hybrid RGO-Sb₂S₃ combines the advantages of individual materials in which Sb₂S₃—acting as a secondary light-harvesting antenna in the visible spectrum—enhances the light absorption of the device, while RGO flakes offer highly conductive multiple charge-transfer percolation paths, suitable for ballistic electron transport to the LUMO of PC₇₁BM.⁵⁷⁶ Moreover, the RGO sheets accelerate charge transfer, hindering the recombination phenomena in inorganic nanocrystals.⁵⁷⁶ Therefore, the resulting cells exhibited a significant η of 7%,



corresponding to an enhancement of $\sim 23\%$ compared to the reference device.⁵⁷⁶ Kim *et al.* recently reported the utilization of size-selected GO flakes as the third component in PTB7:PC₇₁BM-based OSCs.⁵⁷⁸ GO nanosheets with lateral sizes ranging from nanometers to micrometers were fabricated by a physical sonication process.⁵⁷⁷ The physical size of the GO flakes affects the GO dispersion stability and morphological aggregation of the ternary blend.⁵⁷⁷ In particular, it was found that the use of GO with lateral sizes of 500–750 nm maximizes both hole and electron mobilities of ternary OSCs.⁵⁷⁷ Consequently, the non-geminate recombination was reduced. The corresponding ternary OSCs reached an η value as high as 9.21% by increasing the FF to 69.4% in inverted devices, while the reference binary OSCs exhibited an η value of 7.94%.⁵⁷⁷

Other 2D materials have been exploited as additives in OSCs. Bruno *et al.*⁵⁷⁹ used WS₂ nanotubes in P3HT-QDs devices (which can also be classified as an organic–inorganic hybrid SC; see Section 7) as additives. *In situ* laser-induced anchoring of noble-metal NPs onto the surface of thin GO, WS₂, MoS₂, and BN have been developed to design special additives for OSCs.⁵⁸⁰ In particular, WS₂ nanosheet–Au NP assemblies added in PCDTBT:PC₇₁BM allowed the corresponding cells to achieve an $\sim 13\%$ enhancement in η compared to the binary reference.⁵⁷⁹ This effect was attributed to the efficient synergy of plasmon-enhanced absorption of Au NPs and superior charge transport into WS₂ nanosheets, as well as energy-level matching between the polymer and intermediate WS₂ nanosheets.⁵⁷⁹ WSe₂ nanoflakes of different sizes were also used as the third component in ternary PTB7:PC₇₁BM-based OSCs (Fig. 8b).³³⁶

Three WSe₂ samples, with different average lateral sizes (below 20 nm, between 30 and 50 nm, and above 50 nm) were investigated.³³⁶ Upon the introduction of medium-sized flakes, an η value of 9.45% was measured, which is one of highest reported for OSCs based on PTB7 as the polymer donor.³³⁶ The observed enhancement was attributed to the synergistic effect of absorption and charge transfer processes.³³⁶ Notably, only medium-sized WSe₂ flakes contributed to η enhancement.³³⁶ This was linked with the similar size of WSe₂ flakes and PC₇₁BM domains in the ternary blend.³³⁶ Therefore, the insertion of such nanoflakes introduces additional percolation pathways in the photoactive blend, promoting electron extraction and therefore collection.³³⁶ These results highlighted the importance to match the morphological properties of 2D materials with the photoactive components of OSC blends.³³⁶ Lately, Yang *et al.* incorporated LPE-produced black phosphorus nanoflakes (BPNFs) with an average size of 46 nm in poly([2,6'-4,8-di(5-ethylhexylthienyl)benzo[1,2-b;3,3'-b']dithiophene]{3-fluoro-2[(2-ethylhexyl)carbonyl]thieno[3,4-b']thiophenediyl}):low-bandgap NFA (PTB7-Th:IEICO-4F)-based OSCs as the third component.⁵⁸³ BPNFs were used as the morphology modifier to improve the performance of fullerene-free OSCs.⁵⁸² The incorporation of BPNFs promotes molecular ordering and higher phase purity of the ternary blend, contributing to lowering the charge transport resistance and suppressing charge recombination compared to the binary blend without BPNFs.⁵⁸² As a result, ternary OSCs exhibited an η value of 12.2%, whilst the η value of binary OSCs

was 11.4%.⁵⁸² Moreover, the ternary OSC with BPNFs retains 73% of its initial η after thermal treatment at 150 °C in a N₂ atmosphere for over 3 h, while the binary OSC retains only 60% of its initial η under the same condition.⁵⁸² The improvement in stability was ascribed to the retarding of phase mixing in BHJ during the aging period as a consequence of the space confinement effect induced by BPNFs.⁵⁸²

The effect of hydrogenation on MoSe₂ nanosheets, used as additives in PTB7-Th:PC₇₁BM OSCs, was also investigated in ternary devices.⁵⁸⁴ The OSCs exhibited an η value of 10.44%, which represent a 16% increment compared to the reference binary OSCs.⁵⁸³ The obtained results were associated with the establishment of optimized percolation pathways in the active layer.⁵⁸³ Furthermore, the ternary OSC maintained 70% of its initial η value after continuous heating at 100 °C for approximately 1 h.⁵⁸³ The improvement in performance, compared to the reference OSC, was attributed to enhanced exciton generation and dissociation at the MoSe₂–fullerene interfaces and balanced μ_e and μ_h .⁵⁸³ Very recently, chlorine-functionalized graphdiyne has been successfully applied as a multifunctional solid additive to fine-tune the morphology and improve the efficiency and reproductivity of NFA-based OSCs, which reached an η value of 17.3% (certified η of 17.1%).⁵⁸⁵

Table 2 summarizes the main results achieved with OSCs using GRMs as the active layer components.

4.3 CTLs

The most successful application of GRMs for OSCs is in CTLs as either ETLs or HTLs. To design high-efficiency OSCs, ETL/HTL are positioned between the photoactive layer and anode/cathode, to reduce the potential barriers at both the interfaces and suppress the current leakage and/or charge recombination.⁵⁸⁶ Preferably, to ensure ohmic contacts at both interfaces, the ϕ_w value of an ETL should match the LUMO level of the acceptor, while the ϕ_w value of the HTL should match the HOMO level of the donor.⁵⁸⁷

A large number of HTL materials for OSCs have been investigated, including transition metal oxides (*e.g.*, V₂O₅, NiO_x)^{588,589} and self-assembled organic molecules, *e.g.*, poly(3,4-ethylene-dioxythiophene) polystyrene sulfonate (PEDOT:PSS).^{590,591} With regard to ETLs, the most efficient materials currently used are n-type inorganic (*e.g.*, TiO_x and ZnO)⁵⁹² and organic semiconductors.⁵⁹³ However, there are several issues related to the most established CTLs. In particular, the main issues are related to the strong acidic and hygroscopic character of PEDOT:PSS and the sensitiveness of sol-gel-prepared TiO_x to moisture. Therefore, costly manufacturing in a controlled atmosphere is often required.⁵⁹⁴ In addition, charge transporting materials do not always allow ϕ_w tuning and/or solution processability.⁵⁹⁵ In this context, graphene derivatives⁵⁹⁶ and other 2D materials⁵⁹⁷ have been extensively investigated as buffer layers in order to fully exploit their features, including solution processability, low-cost fabrication, environmental stability, and ϕ_w tunability *via* functionalization methods.

HTLs. PEDOT:PSS as well as metal oxides (*e.g.*, V₂O₅, VO_x, MoO_x, and NiO) have been widely used as HTL components in



Table 2 Summary of the PV performance of OSCs using GRMs as the active layer components

Material	Usage	Device structure	Cell performance					Ref.
			J_{sc} (mA cm ⁻²)	V_{oc} (V)	FF (%)	η (%)		
Fullerene-grafted graphene	Electron acceptor	ITO/PEDOT:PSS/P3HT:C ₆₀ -G/Al	4.45	0.56	0.49	1.22	564	
Chemically synthesized GO-ethylene-dinitro-benzoyl (GO-EDNB)	Electron acceptor	ITO/PEDOT:PSS/P3HT:GO-EDNB/Al	3.32	0.72	0.4	0.96	565	
Laser produced GO-ethylene-dinitro-benzoyl (LGO-EDNB)	Electron acceptor	ITO/PEDOT:PSS/PCDTBT:LGO-EDNB/TiO _x /Al	5.29	1.17	0.39	2.41	566	
RGO	Electron acceptor	FTO/TiO ₂ NR-ZnO NP/RGO/P3HT/PEDOT:PSS/Au	10.78	0.68	0.52	3.79	567	
Nitrogen doped graphene (N-RGO)	Additive	ITO/PEDOT:PSS/P3HT:PC ₆₁ BM:N-RGO/Ca/Al	14.90	0.6	0.49	4.50	572	
Graphene flakes	Additive	ITO/PEDOT:PSS/P3HT:PC ₆₁ BM:graphene/Ca/Al	8.00	0.6	0.66	3.17	573	
Functionalized graphene nanoflakes (GNFs)	Additive	ITO/PEDOT:PSS/PCDTBT:PC ₇₁ BM:GNF-EDNB60/TiO _x /Al	12.56	0.89	0.57	6.41	484	
Graphene-based porphyrin molecule (GO-TPP)	Additive	ITO/PEDOT:PSS/PTB7:PC ₇₁ BM:GO-TPP/TiO _x /Al	17.98	0.77	0.61	8.58	574	
Graphene oxide quantum dots (GOQDs)	Additive	ITO/PEDOT:PSS/PTB7:PC ₇₁ BM:GOQD/TiO _x /Al	15.20	0.74	0.68	7.60	575	
RGO-antimony sulfide (RGO-Sb ₂ S ₃) hybrid nanosheets	Additive	ITO/PEDOT:PSS/PCDTBT:PC ₇₁ BM:RGO-Sb ₂ S ₃ /TiO _x /Al	13.47	0.92	0.55	6.81	576	
Medium sized GO	Additive	ITO/ZnO/PTB7:PC ₇₁ BM:MGO/MoO ₃ /Al	18.00	0.74	0.69	9.09	577	
WS ₂ decorated with Au NPs	Additive	ITO/PEDOT:PSS/PCDTBT:PC ₇₁ BM:PCDTBT:WS ₂ -Au/TiO _x /Al	12.3	0.89	0.58	6.30	579	
WSe ₂	Additive	ITO/PFN/PTB7-WSe ₂ -PC ₇₁ BM/MoO ₃ /Al	17.84	0.73	0.72	9.45	336	
BPFNs	Additive	ITO/ZnO/PTB7-Th:IEICO-4F:BPFNs/MoO ₃ /Ag	23.44	0.71	0.73	12.20	582	
Hydrogen plasma-treated MoSe ₂	Additive	ITO/ZnO/PTB7-Th:PC ₇₁ BM/MoO ₃ /Al	18.69	0.78	0.70	10.2	583	
Chlorine-functionalized graphdiyne	Additive	ITO/PEDOT:PSS/PM6:Y6/PFN-Br/Al	26.09	0.84	0.79	17.32	584	
Zn-porphyrin based metal-organic framework nanosheets (Zn ₂ (ZnTCPP))	Additive	ITO/PEDOT:PSS/P3HT:PC ₆₁ BM: Zn ₂ (ZnTCPP):BCP/Al	10.80	0.69	0.69	5.2	581	
Bi ₂ OS ₂ nanosheets	Additive	ITO/ZnO/ITIC:Bi ₂ OS ₂ :PBDT-T/MoO ₃ /Ag	18.61	0.94	0.71	12.31	582	
g-C ₃ N ₄ QDs	Additive	ITO/ZnO/g-C ₃ N ₄ :P3HT:PC ₆₁ BM/PEDOT:PSS/Ag	11.44	0.61	0.60	4.23	278	
		ITO/ZnO/g-C ₃ N ₄ :PBDTTT-C: PC ₇₁ BM/PEDOT:PSS/Ag	15.9	0.70	0.57	6.62		
		ITO/ZnO/g-C ₃ N ₄ :PTB7-Th:PC ₇₁ BM/PEDOT:PSS/Ag	16.74	0.78	0.70	9.2		

order to block electrons as well as transport holes, thus minimizing carrier recombination in OSCs.⁵⁹⁸ Unfortunately, the highly acidic nature of PEDOT:PSS,^{599,600} as well as the high cost of vacuum processes (*e.g.*, ALD) used to deposit inorganic oxide (*e.g.*, ZnO, VO_x) films^{601–603} or the insufficient performance of solution-processed metal oxide films (compared to the organic reference),⁶⁰⁴ pushed research toward the search for solution-processed alternatives. In this context, GO and RGO were found to be effective materials for replacing both PEDOT:PSS and inorganic oxides. In this context, Li *et al.*⁶⁰⁵ reported graphene-based HTL using spin-coated 2 nm-thick GO film to replace PEDOT:PSS in P3HT:PC₆₁BM-based OSCs. The devices with GO exhibited a slower recombination rate and better stability than PEDOT:PSS-based OSCs.⁶⁰⁴ In addition, the PEDOT:PSS-GO composite was investigated as the HTL in PTB7:PC₇₁BM-based OSCs.⁶⁰⁶ The composite layer improved the μ_h value in the presence of benzoid–quinoid transitions, which also provided ϕ_w alignment between GO and PEDOT:PSS.⁶⁰⁵ Consequently, PEDOT:PSS-GO-based OSCs achieved an η value of 8.21%, which was 12% higher than that achieved by PEDOT:PSS-based OSCs.⁶⁰⁵ In ref. 607, two layers of GO and vanadium oxide (VO_x) were subsequently spin coated to yield a hybrid film used as the HTL in PTh4FBT:PC₇₁BM-based OSCs, reaching an η value of 6.7%. The authors demonstrated that thin films of graphene derivatives can improve the electron-blocking properties of the metal-oxide-based HTLs, while offering a barrier against the penetration of metal oxide films

into organic active layers.⁶⁰⁶ Despite the promising results on GO as the HTL, its insulating nature leads to severe limitations for efficient hole transport. Therefore, as a general strategy to improve the HTL performance, GO-based HTLs were modified to a partially reduced GO (pRGO) *via* thermal annealing and chemical and photoreduction processes.⁶⁰⁸ For example, Yun *et al.*⁶⁰⁹ prepared RGO by a novel *p*-toluenesulfonyl hydrazide (*p*-TosNHNH₂) reductant to be used as the HTL in P3HT:PC₆₁BM-based OSCs, reaching an η value of 3.6% (similar to that of the PEDOT:PSS-based reference). Furthermore, the RGO-based OSC exhibited a lifetime significantly longer than that of the PEDOT:PSS-based device.⁶⁰⁸ Similarly, Murray *et al.*⁶¹⁰ photoreduced GO with UV irradiation to obtain a HTL with ϕ_w aligned with the HOMO level of the PTB7 donor (Fig. 9a). It was demonstrated that the resulting pRGO HTL positively influenced the PTB7 π -stacking orientation, promoting the hole extraction process. In addition, although the η value of pRGO-based OSCs (7.5%) was comparable to that of the PEDOT:PSS-based reference, the prolonged lifetime in air highlighted the key advantage of pRGO as the HTL, which is in agreement with other related works.^{608,609} By following a different reduction method, Yeo *et al.*⁶¹¹ produced a RGO HTL by functionalizing GO with *p*-hydrazinobenzene sulfonic acid hemihydrate as the reducing agent. The resulting sRGO has shown both high dispersion concentration in water (without the need of surfactants) and high electrical conductivity (3.18 S cm⁻¹).⁶¹⁰ Moreover, sRGO exhibited a higher ϕ_w value





Fig. 9 (a) Chemical structures of the PTB7 donor polymer, PC₇₁BM acceptor, and GO HTL. Schematic of a standard OSC indicating the location of CTLs. Comparative PV performance of PTB7:PC₇₁BM-based OSC with PEDOT:PSS or GO HTLs. Adapted with permission from ref. 609, Copyright 2011, American Chemical Society. (b) Schematic of the OSC structure. *I*–*V* curves of OSCs based on different HTLs. Adapted from ref. 616. (c) Schematic of the inverted-type OSC incorporating a MoS₂ HTL. Schematic of the structure of the thin-layer MoS₂ buffer layer (side view) and schematic of the monolayer flake of MoS₂ along the 0001 direction (top view). Adapted from ref. 620.

(i.e., 5.04 eV) compared to that of RGO. Therefore, sRGO was compatible with the HOMO level of conventional donor polymers.⁶¹⁰ Further, sRGO was successfully applied in OSCs based on P3HT, poly[1-(6-{4,8-bis[(2-ethylhexyl)oxy]-6-methylbenzo[1,2-*b*:4,5-*b'*]dithiophen-2-yl)-3-fluoro-4-methylthieno [3,4-*b*]thiophen-2-yl)-1-octanone] (PBDTTT-CF), and PTB7 as polymer donors.⁶¹⁰ In particular, an η value higher than 7% was achieved for sRGO-based OSCs, which also exhibited device stability superior to that of the PEDOT:PSS-based reference.⁶¹⁰ Liu *et al.*⁶¹² produced a sulfated RGO by introducing -OSO₃H groups into the basal plane of GO (RGO-OSO₃H). The corresponding RGO-OSO₃H HTL displayed a conductivity as high as 1.3 S m⁻¹ and ϕ_w aligned with the HOMO level of P3HT.⁶¹¹ The corresponding RGO-OSO₃H-based OSC achieved an η value of ~4.37%, which was similar to that obtained for PEDOT:PSS-based reference (4.39%).⁶¹¹

An alternative way to increase the electrical conductivity of GO relies on its mixing with SWCNTs.⁶¹³ This approach allowed P3HT:PC₆₁BM-based OSCs to reach an η value of 4.1%.⁶¹² Furthermore, surfactant-free Au NPs were incorporated between the photoactive layers and GO HTL, leading to an η value increase of ~30% compared to the PEDOT:PSS-based reference.⁶¹⁴ In addition, the GO-based devices retained 50% of their initial η after 45 h of continuous illumination, while the reference devices based on PEDOT:PSS completely degraded after 20 h.⁶¹³ The η enhancement was attributed to an increase in the exciton generation rate caused by Au NP-induced plasmon absorption enhancement. Meanwhile, the stability performance was ascribed to the suppression, in presence of GO, of oxygen and/or In diffusion from ITO toward the P3HT:PC₆₁BM.⁶¹³

Li *et al.*⁶¹⁵ investigated deposited GQDs as the HTL material in DR₃TBDT:PC₇₁BM- and P3HT:PC₆₁BM-based OSCs (DR₃TBDT is a small-molecule donor based on the benzo[1,2-*b*:4,5-*b'*]dithiophene unit).⁶¹⁶ GQD films exhibited homogenous morphology and high conductivity, yielding P3HT:PC₆₁BM-based OSCs with an η value of 3.51%.⁶¹⁵ This value was similar to that measured for

PEDOT:PSS-based OSCs (η = 3.52%).⁶¹⁵ In addition, GQD-based OSCs exhibited longer lifetime and more reproducible η compared to the reference device.⁶¹⁵

An effective approach to enhance the performance of GO-based HTLs is to tune their ϕ_w through functionalization routes.¹¹² In ref. 617, a fluorinated RGO (FRGO) was synthesized with a ϕ_w value of 4.9 eV using a F-containing phenylhydrazine-based reductant. The as-produced FRGO was then used as the HTL in PTB7:PC₇₁BM- and P3HT:ICBA-based OSCs (Fig. 9b).⁶¹⁶ The functionalization process detached oxygen functional groups from GO flakes, while concomitantly doping the edges and basal planes of the flakes themselves with F.⁶¹⁶ Due to the ϕ_w increase, the FRGO-based OSCs exhibited similar performance and higher stability compared to those of the PEDOT:PSS-based reference.⁶¹⁶ A series of GOs with tuned oxidation (pr-GO) were synthesized by Li *et al.*⁶¹⁸ strictly by controlling the preoxidation steps, oxidation time, and oxidant content, leading to ϕ_w values between 4.74 and 5.06 eV. By precisely controlling the oxidation time, a P3HT:PC₆₁BM-based OSC using pr-GO HTL reached an η value of 3.74%, which was ~3.60% higher than that reported for the PEDOT:PSS-based reference.⁶¹⁷ Stratakis *et al.*⁶¹⁹ demonstrated that GO ϕ_w can be effectively tuned by UV laser irradiation in the presence of Cl gas. In particular, by irradiating ultrathin GO films with a pulsed laser in the presence of a dopant Cl precursor gas, a simultaneous reduction and Cl doping of GO lattice was achieved.⁶¹⁸ Following the irradiation process, Cl atoms were linked to both basal planes and edges of GO. The ϕ_w value of GO was tuned by controlling the laser exposure time.⁶¹⁸ In particular, the ϕ_w value of chlorinated GO (GO-Cl) was adjusted from 4.9 eV in GO to a maximum of 5.23 eV in GO-Cl by increasing the laser exposure level up to 60 laser pulses (pulse duration = 20 ns; wavelength = 248 nm; power of 50 mW; beam profile = 20 × 10 mm²).⁶¹⁸ The induced polar character of C–Cl bonds is responsible for the downward shift in E_F in the VB of GO-Cl and the subsequent increase in ϕ_w compared to pristine GO.⁶¹⁸



This ϕ_w tuning determined the energy matching between GO-Cl and the PCDTBT donor, allowing the resulting OSC to reach an η value higher than that of PEDOT:PSS-based reference.⁶¹⁸ Phosphorylated GO was recently used as HTL in PTB7:PC₇₁BM-, PBDBTTT-C:PC₇₁BM-, and P3HT:PC₆₁BM-based OSCs, enhancing their η from 6.28%, 5.07%, and 2.78% (in pristine GO-based devices) to 7.90%, 6.59%, and 3.85%, respectively.⁶²⁰ The proposed phosphate ester modification increased the GO film roughness and hydrophobicity, while the p-doping of the GO increased ϕ_w from 4.24 to 4.70 eV, providing better matching with the HOMO level of the polymer donor.⁶¹⁹

In addition to graphene-based materials, solution-processed TMDs have also been widely investigated as HTL materials. For example, Gu *et al.*⁶²¹ exploited a film of MoS₂ flakes, produced by the chemical Li intercalation method, as the HTL in P3HT:PC₆₁BM- and PTB7:PC₇₁BM-based OSCs. The resulting MoS₂-based OSCs achieved η values of 4.02% and 8.11% for P3HT:PC₆₁BM and PTB7:PC₇₁BM active layers, respectively (Fig. 9c).⁶²⁰ These η values were higher than those measured for the reference OSCs using thermally evaporated MoO₃ HTLs.⁶²⁰

The superior HTL performance of MoS₂ compared to that of vacuum-evaporated MoO₃ was attributed to the inferior trap density compared to the MoO₃ reference, providing higher hole concentration at V_{OC} (*i.e.*, $\sim 10^{16} \text{ cm}^{-3}$ in MoS₂ vs. $\sim 10^{16} \text{ cm}^{-3}$ in MoO₃).⁶²⁰ In addition, at the MoS₂/P3HT interface, the presence of a surface dipole with the negative charge end pointing toward the active film electrode and positive charge end pointing toward the Ag electrode reinforces the actual built-in potential across the device, suppressing charge recombination and leading to a more effective charge extraction capability.⁶²⁰ Likewise, Yun *et al.* prepared a p-type MoS₂ (p-MoS₂) layer by HAuCl₄·3H₂O doping.⁶²² This process increased the MoS₂ ϕ_w value from 4.52 to 4.76 eV.⁶²¹ As a result, P3HT:PC₆₁BM-based OSCs using p-MoS₂ HTL exhibited an η value of 3.4%, which was higher than that of pristine MoS₂-based OSCs ($\eta = 2.8\%$), owing to the better energy-level matching between the P3HT HOMO level and HTL ϕ_w .⁶²¹ In the research activity of energy-level optimization of HTL, Le *et al.* further increased the ϕ_w value of MoS₂ up to 4.9 eV by UV/ozone (UVO) treatment, providing excellent matching with the HOMO level of P3HT ($\sim 5 \text{ eV}$).⁶²³ The resulting MoS₂-based OSCs achieved an η value of 2.44%, which was similar to that of the PEDOT:PSS-based reference ($\eta = 2.81\%$).⁶²² Moreover, the use of MoS₂ HTL extended the device stability in air by protecting the ITO surface from the hygroscopic nature of PEDOT:PSS.⁶²² An increase in MoS₂ ϕ_w was also achieved by introducing O atoms inside the lattice of MoS₂ flakes (O-MoS₂) *via* UVO post-treatment.⁶²⁴ The optimized O-MoS₂ flakes were used as HTLs in PTB7:PC₇₁BM-based OSCs, which displayed an η value of 7.64%—53% higher than that of the cell using pristine MoS₂ and comparable to that obtained using PEDOT:PSS (7.6%).⁶²³ In addition, the R_s value of the device with O-MoS₂ was considerably lower ($1.88 \Omega \square^{-1}$) than that obtained using MoS₂ ($4.03 \Omega \square^{-1}$).⁶²³ The incorporation of O atoms into the MoS₂ lattice can act as a type of doping or alloy, reducing structural defects by the filling of vacancies, as well as increasing ϕ_w (up to 4.93 eV) to match the HOMO level of P3HT.⁶²³ Liu *et al.* proposed a further surface modification

pathway of MoS₂ with a hydrophilic surfactant *via* electrostatic interaction.⁶²⁵ Subsequently, they fabricated PTB7:PC₇₁BM-based OSCs with a modified MoS₂ HTL, achieving $\eta > 7\%$.⁶²⁴ Yang *et al.* decorated MoS₂ flakes with Au NPs in order to create localized surface plasmon resonance effects to boost η .⁶²⁶ In fact, Au NPs act as plasmonic near-field antennas,^{627,628} increasing the absorption cross-section of the photoactive layer.⁶²⁵ As a result, PTB7:PC₇₁BM-based OSCs using the MoS₂-Au hybrid as the HTL, exhibited an η value of 7.25%, which represents a 17.3% increase compared to that of pristine MoS₂ HTL-based devices ($\eta = 6.18\%$).⁶²⁵ Zheng *et al.* proposed a graphene–MoS₂ heterostructure (GMo) as an interlayer between the ITO and PEDOT:PSS HTL in OSCs based on a binary PTB7-Th:PC₇₁BM system.⁶²⁹ GMo was hydrothermally synthesized using thiourea/glycerol, LPE-produced graphene, and phosphomolybdic acid as the precursors.⁶²⁸ The few layers of oxygen-incorporated MoS₂ contained both 2H and 1T phases.⁶²⁸ GMo-based OSCs reached $\eta = 9.5\%$, while retaining more than 93% of the initial η over 1000 h.⁶²⁸ Beyond MoS₂, other TMDs have been investigated as HTLs. Kwon *et al.* used WS₂ treated with UVO as the HTL in P3HT:PC₆₁BM-based OSCs.⁶³⁰ The UVO treatment modified the ϕ_w value of WS₂ from 4.75 to 4.95 eV, improving the alignment with the LUMO level of P3HT in addition to the removal of surface contaminants.⁶²⁹ The combination of these effects allowed the achievement of $\eta = 3.08\%$ (comparable to that of the PEDOT:PSS-based reference (3.23%)).⁶²⁹ UVO treatment was also used for TaS₂ nanosheets, used both as the HTL and ETL in P3HT:PC₆₁BM-based OSCs.⁶³¹ The ϕ_w value of TaS₂ changed from 4.4 eV to 5.1 eV and $\eta = \sim 3.06\%$ could be achieved. This value was similar to that measured for the PEDOT:PSS-based OSCs as the reference (3.28%).⁶²⁹ Gu *et al.* introduced NbSe₂ HTL in inverted PTB7:PC₇₁BM- and P3HT:PC₆₁BM-based OSCs, reaching η of $\sim 8.10\%$ and $\sim 3.05\%$, respectively.⁶³² These η values were higher than those of OSCs based on vacuum-deposited MoO₃ (7.54%) and spin-coated PEDOT:PSS (2.7%).⁶³¹

The enhancement of η was attributed to the flake-like 2D structure, which exhibits a lower trap density, as well as to the existence of surface dipoles, which promote charge extraction processes. Lastly, layered bismuth selenide nanoplatelets (L-Bi₂Se₃) were implemented as the HTL in inverted P3HT:PC₆₁BM-based OSCs.⁶³³ The corresponding OSCs reached $\eta = 4.37\%$, which was higher than the η value of OSCs based on evaporated MoO₃ HTL (3.91%).⁶³² The η improvement was ascribed to the high conductivity of L-Bi₂Se₃.⁶³² Moreover, the L-Bi₂Se₃ ϕ_w was found to increase with aging under the ambient conditions due to O-induced p-doping, resulting in improved V_{OC} and FF.⁶³² More recently, Li *et al.* demonstrated the use of LPE-produced few-layer WS₂ and MoS₂ nanosheets as the HTL materials for high-efficiency NFA-based OSCs (Fig. 10).⁶³⁴ The cells used Y6⁴⁷¹ or IT-4F⁶³⁵ as small-molecule NFAs and PBDB-T-SF⁶³⁶ or PBDB-T-2F⁶³⁴ as the polymer donors. Binary PBDB-T-SF:IT-4F and ternary PBDB-T-2F:Y6:PC₇₁BM OSCs based on WS₂ as the HTL exhibited an η value of 15.8% and 17.0%, respectively, which were higher than the corresponding reference OSCs based on PEDOT:PSS, *i.e.*, η of 13.5% and 16.4%, respectively.⁶³³ The observed performance enhancement was attributed to a reduction in bimolecular recombination losses (*i.e.*, losses determined by the recombination of an



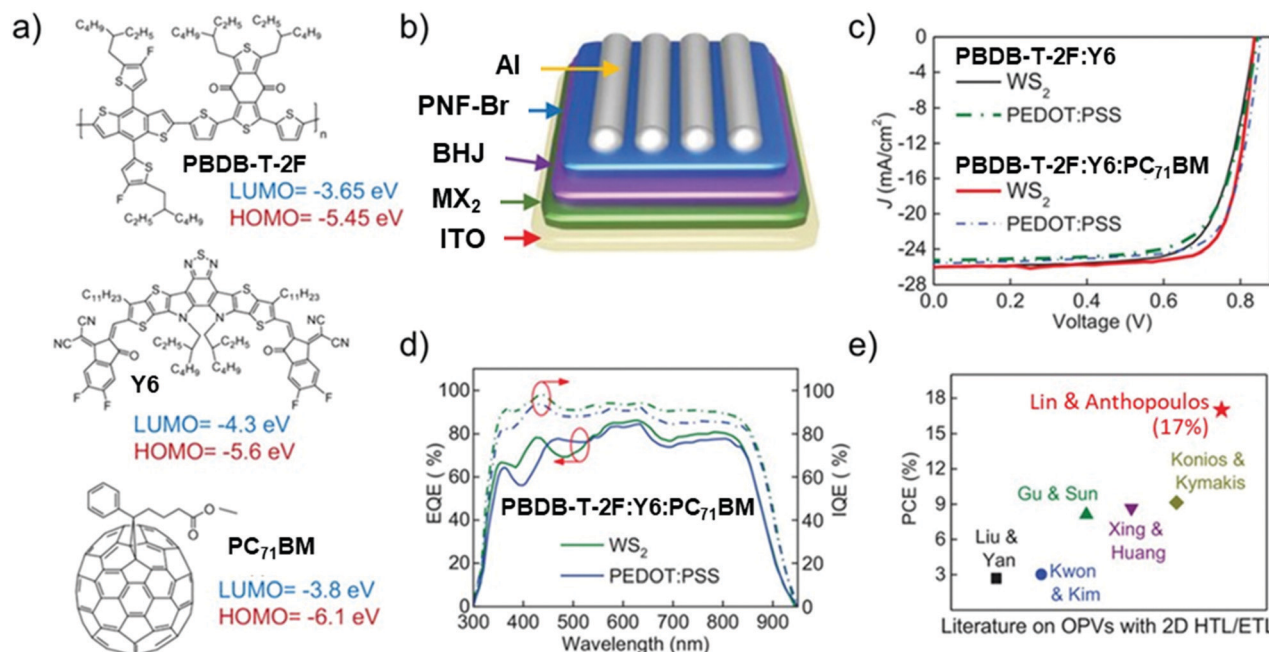


Fig. 10 (a) Chemical structure of PBDB-T-2F, Y6, and PC₇₁BM and the corresponding LUMO and HOMO energies. (b) Schematic of the standard OSC architectures employed. (c) *J*-*V* curves of OSCs based on PBDB-T-2F:Y6 and PBDB-T-2F:Y6:PC₇₁BM with different HTLs. (d) EQE curves of OSCs based on a PBDB-T-2F:Y6:PC₇₁BM active layer for different HTLs. (e) A comparison of the performances of previously reported OSCs with 2D material interfaces. Adapted from ref. 633.

electron with a hole, thus directly depending on both electron and hole concentrations) compared to PEDOT:PSS-based OSCs.⁶³³ The lower bimolecular recombination in WS₂-based devices compared to MoS₂ and PEDOT:PSS devices was ascribed to the deeper ϕ_W value of WS₂ on ITO (*i.e.*, 5.5 eV vs. 5.4 eV and 4.8 eV for MoS₂ and PEDOT:PSS on ITO, respectively).⁶³³ The optimal WS₂ ϕ_W allowed charge collection to be improved and surface energy to be reduced, leading to quasi-ideal phase separation.⁶³³

Table 3 summarizes the main results achieved with OSCs using HTLs based on GRMs.

ETLs. For the use of GRMs as ETLs, proper functionalization routes have been used to decrease the ϕ_W values close to that of the HOMO level of fullerene acceptors, aiming to facilitate efficient electron transport from the electron acceptor to the ETL. Liu *et al.* first reported GRM-based ETLs based on Cs₂CO₃-functionalized GO in P3HT:PC₆₁BM-based OSCs.⁶³⁷ By replacing the -COOH groups of GO with -COOCs groups through charge neutralization, ϕ_W was decreased from 4.7 to 4.0 eV. Consequently, ϕ_W of Cs₂CO₃-functionalized GO matched the LUMO level of PC₆₁BM, thereby facilitating electron collection.⁶³⁶ An η value of 3.67% and 2.97% were obtained using normal and inverted OSC structures, respectively.⁶³⁶ The PV performance were similar to those measured for the reference cell using LiF as the standard ETL.⁶³⁶

Similar Cs₂CO₃-based functionalization was applied to GQDs (GQDs-Cs₂CO₃), which were then used as the ETL in inverted P3HT:PC₆₁BM-based OSCs.⁶³⁸ The OSCs exhibited an η value of 3.23%, which was 56% higher than that of OSCs using pristine Cs₂CO₃ HTL.⁶³⁷ In addition, while GQDs-Cs₂CO₃-based devices

retained 50% of their original η under ambient conditions (exposition for 1200 h), the η value of pristine Cs₂CO₃-based device decreased to 17% of its initial value.⁶³⁷ The high η and stability of GQDs-Cs₂CO₃-based OSCs were attributed to both optimal electron extraction and suppression of leakage current, as well as the immobilization of Cs⁺ ions on GQDs in the HTL, delaying their diffusion into the P3HT.⁶³⁷ Meanwhile, n-doped GO was produced through chemical Li intercalation, leading to functionalized GO-Li with ϕ_W of 4.3 eV.⁶³⁹

The low ϕ_W value of GO-Li was ascribed to the presence of Li atoms with low electronegativity.⁶³⁸ In detail, Li atoms bonded to GO release their valence electrons to GO, leading to the formation of an electric dipole induced by Li⁺.⁶³⁸ The charge transfer from Li to GO plane shifts the Fermi level toward the vacuum, inducing a difference between the Fermi level of the two materials of 0.67 eV, explaining the decrease of ϕ_W .⁶³⁸ In PCDTBT:PC₇₁BM-based OSCs, the GO-Li layer, which is inserted between TiO_x and photoactive blend, acts as an interfacial engineering material, increasing η up to 6.29% (4.89% in GO-based OSCs and 5.51% in interlayer-free OSCs).⁶³⁸ These results prove the bifunctional role of GO-Li acting as (1) an interfacial engineering material that improves the ohmic contact between the cathode and the ETL, while increasing the internal electric field amplitude;⁶³⁸ (2) a protection layer against humidity and oxygen, enhancing the device stability during prolonged illumination.⁶³⁸

Beyond the intercalation of alkali metals in GO, an alternative n-doping strategy of RGO was developed by producing RGO-ZnO and RGO-TiO₂ nanocomposites, which were then

Table 3 Summary of the PV performance of OSCs using GRMs as the HTL

Material	Usage	Device structure	Cell performance				Ref.
			J_{SC} (mA cm ⁻²)	V_{OC} (V)	FF (%)	η (%)	
GO	HTL	ITO/ZnO/PTh4FBT:PC ₇₁ BM/VO _x /GO/Ag	13.2	0.76	0.67	6.7	606
Partial reduced GO	HTL	ITO/pr-GO/PCDTBT-PC ₇₁ BM/TiO _x /Al	11.18	0.89	0.59	5.96	607
UV-O ₃ treated GO	HTL	ITO/UV-O ₃ treated GO/PTB7:PC ₇₁ BM/LiF/Al	15.21	0.72	0.68	7.39	609
Sulfonic acid-functionalized RGO	HTL	ITO/sr-GO/PTB7:PC ₇₁ BM/Ca/Al	15.3	0.75	0.63	7.18	610
GO-SWCNT	HTL	ITO/GO-SWCNT/P3HT:PC ₆₁ BM/Ca/Al	10.82	0.6	0.63	4.1	612
GQDs	HTL	ITO/GO/P3HT:PC ₆₁ BM/Ca/Al	10.20	0.52	0.66	3.51	614
Fluorine-functionalized RGO	HTL	ITO/FRGO/P3HT:PC ₆₁ BM/Ca/Al	8.78	0.6	0.7	3.64	616
Partial oxidized GO (pr-GO)	HTL	ITO/pr-GO/P3HT:PC ₆₁ BM/LiF/Al	10.40	0.61	0.59	3.74	617
Photochlorinated GO (GO-Cl)	HTL	ITO/GO-Cl/PCDTBT:PC ₇₁ BM/TiO _x /Al	13.65	0.88	0.55	6.56	618
Phosphorylated GO	HTL	ITO/P-GO/PTB7:PC ₇₁ BM/Ca/Al	16.12	0.71	0.68	7.9	619
MoS ₂	HTL	ITO/ZnO/PTB7:PC ₇₁ BM/MoS ₂ /Ag	15.9	0.72	0.71	8.11	620
p-Doped MoS ₂	HTL	ITO/p-doped MoS ₂ /P3HT:PC ₆₁ BM/Ca/Al	8.62	0.59	0.66	3.38	621
UV/ozone-treated MoS2 (UVO MoS ₂)	HTL	ITO/UVO MoS ₂ /P3HT:PC ₆₁ BM/LiF/Al	7.97	0.52	0.68	2.81	622
Oxygen-incorporated chemical exfoliated MoS ₂ (O-ceMoS ₂)	HTL	ITO/O-ceMoS ₂ /PTB7:PC ₇₁ BM/PFN/Al	14.98	0.73	0.7	7.64	623
Modified ce-MoS ₂ (m-MoS ₂)	HTL	ITO/m-MoS ₂ /PTB7:PC ₇₁ BM/PFN/Al	14.71	0.73	0.67	7.26	624
MoS ₂ decorated with Au NPs (MoS ₂ @Au)	HTL	ITO/MoS ₂ @Au/PTB7:PC ₇₁ BM/PFN/Al	15.44	0.72	0.65	7.25	625
Graphene-MoS ₂ /PEDOT:PSS	HTL	ITO/Graphene-MoS ₂ /PEDOT:PSS/PTB7-Th:PC ₇₁ BM/Ca/Ag	17.2	0.77	0.72	9.4	628
UV-O ₃ treated MoS ₂	HTL	ITO/UV-O ₃ treated MoS ₂ /P3HT:PC ₆₁ BM/LiF/Al	7.81	0.6	0.63	2.96	629
UV-O ₃ treated WS ₂	HTL	ITO/UV-O ₃ treated WS ₂ /P3HT:PC ₆₁ BM/LiF/Al	7.87	0.61	0.64	3.08	629
UV-O ₃ treated TaS ₂	HTL	ITO/TaS ₂ /P3HT:PC ₆₁ BM/LiF/Al	7.87	0.61	0.64	3.06	630
NbSe ₂ nanosheets	HTL	ITO/ZnO/PTB7:PC ₇₁ BM/NbSe ₂ /Ag	16.04	0.72	0.7	8.1	631
Layered bismuth selenide (1-Bi ₂ Se ₃) nanoplates	HTL	ITO/ZnO/P3HT:PC ₆₁ BM/L-Bi ₂ Se ₃ /Ag	9.91	0.65	0.68	4.37	632
WS ₂	HTL	ITO/WS ₂ /PBDB-T-SF:IT-4F/PFN-Br/Al	20.6	0.88	0.74	13.5	633
WS ₂	HTL	ITO/WS ₂ /PBDB-T-2F: Y6: PC ₇₁ BM/PFN-Br/Al	26	0.84	0.78	17	633
UV treated Ti ₃ C ₂ T _x	HTL	ITO/UV-MXene/PBDB-T:ITIC/Ca/Al	15.98	0.89	0.64	9.02	651
GO	HTL	ITO/GO/P3HT:PC ₆₁ BM/GOCs/Al	10.30	0.61	0.59	3.67	636
GO-Cl	HTL	ITO/GO-Cl/PTB7:PC ₇₁ BM/GO-Li/TiO _x /Al	19.59	0.76	0.62	9.14	650
PEDOT:PSS-GO	HTL	ITO/PEDOT:PSS-GO/PM6:Y6/PDINO-G/Al	25.65	0.85	0.76	16.5	652
PEDOT:PSS:GO	HTL	ITO/PEDOT:PSS/SPGO/PTB7:PC ₇₁ BM/Al	17.3	0.67	0.41	4.82	640
g-C ₃ N ₄ -doped PEDOT:PSS	HTL	ITO/g-C ₃ N ₄ -doped PEDOT:PSS/PM6:Y6/PFN-Br/Ag	26.71	0.84	0.73	16.38	641
α -In ₂ Se ₃ nanosheets	HTL	ITO/ α -In ₂ Se ₃ /PBDB-T:ITIC/Ca/Al	16.69	0.88	0.65	9.58	642
WS ₂ nanosheets	HTL	ITO/WS ₂ /PBDB-T-2F:Y6:PC ₇₁ BM/PFN-Br/Ag	26.0	0.83	0.72	15.6	643
MoS ₂ nanosheets	HTL	ITO/WS ₂ /PBDB-T-2F:Y6:PC ₇₁ BM/PFN-Br/Ag	25.3	0.81	0.71	14.9	642

used as the ETL in inverted PTB7:PC₇₁BM-based OSCs.⁶⁴⁴ The RGO-ZnO- and RGO-TiO₂-based OSCs achieved η values of 7.50% and 7.46%, respectively.⁶⁴³ These values were comparable to those obtained using pristine ZnO (7.39%) and TiO₂ (7.22%).⁶⁴³ The authors also compared their RGO-metal oxide (MO)-based OSCs with devices containing thermally evaporated bathocuproine (or 2,9-dimethyl-4,7-diphenyl-1,10-phenanthroline) (BCP) as ETLs, obtaining fairly comparable η (7.47%) due to the capability of RGO to balance hole and electron mobilities of the devices.⁶⁴³ Subsequently, RGO-MO ETLs were also exploited in PCDTBT:PC₇₁BM-based,⁶⁴⁵ P3HT:PC₆₁BM-based,⁶⁴⁶ and low-bandgap quinoxaline-based D-A copolymer:PCBM-based⁶⁴⁷ OSCs.

A RGO-PC₆₁BM composite was produced by Qu *et al.* by anchoring PC₆₁BM onto GO through a pyridine moiety to be used as the ETL in P3HT:PC₆₁BM-based OSCs.⁶⁴⁸ The RGO-PC₆₁BM nanocomposite exhibits higher solubility compared to RGO and a low ϕ_W value of 4.4 eV, which matched the LUMO level of the electron acceptor.⁶⁴⁷ Therefore, the modified PC₆₁BM OSCs significantly improved the η value (3.89%) compared to OSCs using pristine RGO or pyrene-PC₆₁BM ETLs.⁶⁴⁷

Hu *et al.* used GQDs functionalized with ammonium iodide at the edge as a thickness-insensitive ETL with high optical transparency.⁶⁴⁹ PCDTBT:PC₇₁BM-based OSCs using functionalized

GQDs exhibited an η value of 7.49%, which was significantly higher than that of the reference cells using calcium as the ETL.⁶⁴⁸ Importantly, the performance of OSCs was insensitive to the thickness of the GQD layer (*i.e.*, 2–22 nm).⁶⁴⁸

Solution-processed BP flakes in ethanol were also recently demonstrated as an effective interfacial layer between the ZnO ETL and PTB7:PC₇₁BM active layer in inverted OSCs.⁶⁵⁰ The addition of the BP interlayer enhanced the η value by 11%, reaching the maximum value of 8.25%.⁶⁴⁹ The improvement of η was attributed to the formation of a cascaded band structure between PC₇₁BM, ZnO, and BP flakes, which facilitates the electron transport and suppresses the carrier recombination near the cathode.⁶⁴⁹ Furthermore, the BP-incorporated OSC has shown superior air stability, exhibiting a degradation of 5.82% after two days, compared to the reference device, which exhibited a degradation of 9.29% in the same timeframe.⁶⁴⁹ Konios *et al.* demonstrated the simultaneous use of ϕ_W -tuned functionalized GO derivatives as both HTL and ETL in PCDTBT:PC₇₁BM- and PTB7:PC₇₁BM-based OSCs.⁶⁵¹ The ϕ_W tuning of GO took place by either photochlorination⁶¹⁸ or Li neutralization⁶³⁸ for ϕ_W increase or decrease, respectively. Consequently, it was possible to match the GO-Cl ϕ_W with the HOMO level of both PCDTBT and PTB7 donor, as well as GO-Li ϕ_W with the fullerene LUMO



level, enabling the balance between μ_e and μ_h .⁶⁵⁰ As a result, both graphene-based OSCs significantly outperformed the reference ones, leading to η improvement of 30% and 19% for PCDTBT- and PTB7-based devices, respectively.⁶⁵⁰ In particular, the champion device exhibited an η value of 9.14%, which was a record-high value for OSCs using a graphene-based buffer layer.⁶⁵⁰ In the same context, Yu *et al.* demonstrated the use of ϕ_W -tuned MXenes, particularly $\text{Ti}_3\text{C}_2\text{T}_x$, as both HTL and ETL in NFA-based OSCs using PBDB-T:ITIC as the active layer.⁶⁵² The ϕ_W tuning took place through UVO or hydrazine treatments for ϕ_W increase and decrease, respectively.⁶⁵¹ Therefore, the ϕ_W value was tuned in the 4.08–4.95 eV range.⁶⁵¹ The ϕ_W modification mechanism was ascribed to the oxidation or reduction of the C element of $\text{Ti}_3\text{C}_2\text{T}_x$ by UVO or N_2H_4 , respectively.⁶⁵¹ The UVO- and N_2H_4 -treated MXenes were used as the HTLs in conventional OSCs and as the ETL in inverted OSCs, respectively.⁶⁵¹ The resulting cells exhibited an η value of 9.02% or 9.06% respectively, both comparable to the performance achieved with PEDOT:PSS-based references.⁶⁵¹ Pan *et al.* developed an n-doped graphene ETL for OSCs by adding micromechanically exfoliated single-layer graphene to (*N,N*-dimethyl-ammonium *N*-oxide)propyl perylene diimide (PDINO).⁶⁵³ The conductivity of graphene was increased by n-doping with the nitroxide radical of *N*-oxide in PDINO.⁶⁵² The resultant n-doped graphene (PDINO-G) possessed increased conductivity, lower ϕ_W , reduced charge recombination, and increased charge extraction rate compared to pristine PDINO.⁶⁵² The OSCs based on PTQ10:IDIC-2F with PDINO-G as the ETL exhibited an η value of 13.01%, which was superior to that achieved by OSCs without graphene.⁶⁵² Furthermore, PM6:Y6-based OSCs using PEDOT:PPS-GO as the HTL and PDINO-G as the ETL displayed an η value as high as 16.52%, significantly higher than that for OSCs without GO and graphene (15.1%).⁶⁵² The observed performance enhancement was attributed to the higher (by two orders of magnitude) conductivity of graphene-based ETL compared to that of graphene-free ETL, suitable ϕ_W , and optimal charge extraction.⁶⁵²

More recently, Lee *et al.* used MoS_2 nanoflakes, with an average diameter of 27 nm, as an effective electron transporting

interlayer between polyethylenimine ethoxylated (PEIE) and the photoactive layer in OSCs.⁶⁵⁴

MoS_2 nanoflakes acted not only as an ETL but also as a sub-photosensitizer (*i.e.*, additional light-absorbing layer), enhancing η by 27%, 11%, and 15% compared to P3HT:PC₆₁BM-, PTB7:PC₇₁BM-, and PTB7-Th:PC₇₁BM-based reference cells, respectively.⁶⁵³ The observed performance enhancement was attributed to effective electron transport *via* MoS_2 nanoflakes supported by an increased Förster resonance energy transfer^{375,655,656} efficiency of 67% from PTB7:PC₇₁BM to MoS_2 nanoflakes.⁶⁵³

Table 4 summarizes the main results achieved with OSCs using ETLs based on GRMs.

Interconnection layers (ICLs). Tandem OSCs stack two or more single-junction sub-cells (with complementary E_g values) to harvest light from the entire solar spectrum.⁶⁵⁷ Ideally, the V_{OC} value of the tandem devices is the sum of the V_{OC} values of the sub-cells, while the I_{SC} value is the lowest I_{SC} of the two sub-cells, the latter being in series.

An ICL collects electron and holes from the respective sub-cells, acting as a recombination site between them.^{658,659} Therefore, ICL is a critical component in tandem architectures. In addition, an optimal ICL should be uniform, transparent, highly conductive, and resistant to solvents.⁶⁶⁰ So far, PEDOT:PSS/ TiO_2 ,⁶⁶¹ PEDOT:PSS:ZnO,⁶⁶² and LiF/Al/Au/PEDOT:PSS⁶⁶³ have been the most established ICLs, despite the well-known drawbacks attributable to the acidic and aqueous nature of PEDOT:PSS, which have a huge impact on OSC stability.⁶⁶⁴ In the development of ICL, GRMs have been used both to improve the stability of PEDOT:PSS and in combination with other materials as an alternative to PEDOT:PSS.

Tung *et al.* used GO:PEDOT:PSS nanocomposite as the ICL in a tandem OSCs consisting of two identical P3HT:PC₆₁BM-based sub-cells.⁶⁶⁵ The tandem OSCs were fabricated by a direct adhesive lamination process enabled by the sticky GO:PEDOT film.⁶⁶⁴ An η value of 4.14 and V_{OC} of 0.94 V ($\sim 84\%$ of the sum of the V_{OC} of the two sub-cells) were reported.⁶⁶⁴ Surprisingly, the presence of GO in the composite increased the PEDOT:PSS electrical conductivity by altering its chain conformation and

Table 4 Summary of the PV performance of OSCs using GRMs as the ETLs

Material	Usage	Device structure	Cell performance				Ref.
			J_{SC} (mA cm ⁻²)	V_{OC} (V)	FF (–)	η (%)	
GO & Cs-neutralized GO (GOCs)	ETL	ITO/GO/P3HT:PC ₆₁ BM/GOCs/Al	10.30	0.61	0.59	3.67	650
Cs ₂ CO ₃ functionalized GQDs-Cs ₂ CO ₃)	ETL	ITO/GQDs-Cs ₂ CO ₃ /P3HT:PC ₆₁ BM/V ₂ O ₅ /Au	9.18	0.58	0.61	3.23	637
Lithium-neutralized GO (GO-Li)	ETL	ITO/PEDOT:PSS/PCDTBT:PC ₇₁ BM/GO-Li/TiO _x /Al	12.51	0.89	0.57	6.29	638
ZnO-RGO hybrids	ETL	ITO/PEDOT:PSS/PTB7:PC ₇₁ BM/ZnO-RGO/Al	15.19	0.72	0.69	7.5	643
TiO ₂ -RGO hybrids	ETL	ITO/PEDOT:PSS/PTB7:PC ₇₁ BM/TiO ₂ -RGO/Al	14.99	0.74	0.67	7.46	643
TiO _x -RGO composites	ETL	ITO/rGO:TiO _x /P3HT:PC ₆₁ BM/MoO ₃ /Ag	9.85	0.64	0.61	3.82	646
RGO-pyrene-PC ₆₁ BM	ETL	ITO/PEDOT:PSS/P3HT:PC ₆₁ BM/RGO-pyrene-PC ₆₁ BM/Al	9.78	0.64	0.62	3.89	647
GQDs functionalized with ammonium iodide (GQD-NI)	ETL	ITO/PEDOT:PSS/PCDTBT:PC ₇₁ BM/GQD-NI/Al	10.98	0.93	0.73	7.49	648
n-Doped MoS ₂	ETL	ITO/n-doped MoS ₂ /P3HT:PC ₆₁ BM/PEDOT:PSS/Ag	8.16	0.59	0.55	2.73	621
Black phosphorus (BP)	ETL	ITO/ZnO/BP/PTB7:PC ₇₁ BM/MoO ₃ /Ag	18.78	0.72	0.61	8.25	649
N ₂ H ₄ treated Ti ₃ C ₂ T _x	ETL	ITO/N ₂ H ₄ -Ti ₃ C ₂ T _x /PBDB-T:ITIC/MoO ₃ /Al	17.36	0.87	0.6	9.06	651
Small sized MoS ₂	ETL	ITO/PEIE/MoS ₂ /PTB7-Th:PC ₇₁ BM/MoO ₃ /Ag	17.02	0.8	0.66	9.08	653
GO-Li	ETL	ITO/GO-Cl/PTB7:PC ₇₁ BM/GO-Li/TiO _x /Al	19.59	0.76	0.62	9.14	650
PDINO-G	ETL	ITO/PEDOT:PSS-GO/PM6:Y6/PDINO-G/Al	25.65	0.85	0.76	16.5	652



Table 5 Summary of the PV performance of tandem OSCs using GRM-based ICLs

Material	Usage	Device structure	Cell performance				Ref.
			J_{sc} (mA cm ⁻²)	V_{OC} (V)	FF (-)	η (%)	
GO:PEDOT:PSS composite	ICL	Glass/ITO/PEDOT:PSS/P3HT:PC ₆₁ BM/ZnO/GO:PEDOT:PSS/P3HT:PC ₆₁ BM/Ca/Al	7.2	1	0.58	4.14	490
GO	ICL	Glass/ITO/GO/PSEHTT:ICBA/TiO ₂ /GO/PSBTBT:PC ₇₁ BM/ZnO/Al	8.23	1.62	0.63	8.4	491
Cesium neutralized GO (GO-Cs) & GO	ICL	Glass/ITO/PEDOT:PSS/PCDTBT:PC ₇₁ BM/GO-Cs/Al/GO/MoO ₃ /PCDTBT:PC ₇₁ BM/Ca/Al	5.03	1.69	0.46	3.91	492

morphology. Moreover, GO increased the PEDOT:PSS dispersion viscosity, leading to a beneficial effect on the adhesion properties.⁶⁶⁴ Overall, the addition of GO effectively improved charge extraction at the interface between the HTL and active layer.⁶⁶⁴

Yusoff *et al.* incorporated a GO/TiO₂ recombination layer into a tandem OSC.⁴⁹¹ The overall V_{OC} (1.62 V) was approximately the sum of those of the individual sub-cells (0.94 V and 0.68 V).⁴⁹¹ This result indicated that the incorporation of GO in traditional recombination layers can allow the realization of ideal resistance-free interconnection between the front and rear cell, while preserving the optical transparency of the same recombination layers (*e.g.*, TiO₂).⁴⁹¹ Notably, all the tandem OSCs were solution-processed and stable.⁴⁹¹ Finally, Cs-functionalized GO was used in GO-Cs/Al/GO/MoO₃ ICL between two PCDTBT-based sub-cells.⁶⁶⁶ The ICL based on GO promoted recombination between the electrons and holes generated from the front and rear cells, owing to the energy-level matching of the interfaced materials.⁶⁶⁵ In fact, after MoO₃ modification, the ϕ_w value of GO increased up to 5.3 eV, matching the HOMO level of PCDTBT, while that of Al-modified GO-Cs decreased to 4 eV, matching the LUMO level of PCBM.⁶⁶⁵ The resulting η and V_{OC} values were 3.91% and 1.69 V, respectively.⁶⁶⁵ The V_{OC} was almost equal to the sum of the two sub-cells, proving the beneficial role of GRM-based ICLs.⁶⁶⁵

Table 5 summarizes the main results achieved with tandem OSCs using ICLs based on GRMs.

4.4 Summary and outlook

The effort for OSC commercialization has recently seen a renaissance after the development of BHJ single-junction devices based on low-bandgap polymer donors and NFAs,^{474–476} which reached η values exceeding 17%,^{474–476} up to the record value of 18.3%.⁴⁷⁷ Importantly, the LCOE for organic solar modules with an η value of 10% in a 20 year range has recently been estimated to be between 0.185 and 0.486 ¥ kW h⁻¹ (*i.e.*, between 2.7 and 7.3 US cent kW h⁻¹),⁶⁶⁷ which is competitive with the LCOEs afforded by current PV technologies (less than 5 US cents kW h⁻¹)^{131–133} and fossil fuels.^{134,135} In this context, the incorporation of solution-processed 2D materials enabled the OSCs to further increase their performance up to η values of more than 17%.^{584,633} In ref. 633, this achievement was attained by replacing a traditional HTL, *i.e.*, hygroscopic PEDOT:PSS, with solution-processed WS₂ flakes. More generally, several solution-processed GRMs have been proven to combine all the key attributes required by ideal CTLs and/or buffer layers for OSCs. In particular, the energy levels of 2D materials can be tuned on demand to conceive

advanced interface engineering at the device heterojunctions, enhancing the exciton dissociation, while providing optical transparency and high carrier mobilities for efficient charge transport toward the electrodes. Meanwhile, solution-processed 2D materials have tunable energy levels to act as an additive in ternary blends together with NFAs and low-bandgap polymer donors. In addition, solution-processed 2D materials have been demonstrated to regulate the morphology of the active layer, improving device η (up to 17.3%) as well as reproducibility.⁵⁸⁴ Therefore, we are looking forward to seeing the implementation of 2D materials into the most efficient reported OSC architectures to achieve η over 20% in the near future.⁶⁶⁸

Despite the progress seen in 2D materials as CTLs, additives for photoactive layers, and buffer layers, the printing of 2D materials over a large scale in air using either R2R or sheet-to-sheet (S2S) processes is still unreported for the practical realization of large-area (>1 cm²) OSCs and modules.^{669–673} The establishment of scalable LPE methods for the production of 2D materials with controlled size and thickness can stimulate research toward the realization of commercially competitive large-area OSC technologies, including flexible devices, with η exceeding 14%.^{674–678}

Moreover, OSCs based on solution-processed 2D materials can find applications for solution-processed tandem PVs.⁶⁷⁹ For example, the latter can be fabricated using a PSC and OSC as the sub-cells, both produced through R2R methods. The solution processability of efficient tandem SCs is a very attractive alternative to perovskite/Si tandem SCs,⁶⁷⁸ which recently gained enormous interest for off-grid power generation.⁶⁸⁰ In the scenario involving flexible and bifacial OSCs, (semi)transparent and flexible electrodes based on solution-processed graphene and graphene derivatives are still not competitive with commercially established TCO-based technologies (see additional discussion in Section 8). Lastly, OSCs are attractive for indoor applications,^{681–683} such as ideal power sources for indoor IoT devices. In this context, η over 21% has been reached,^{680,682} and the exploitation of 2D materials may rapidly contribute toward further improving these performances.

Overall, we believe that the use of cost-effective solution-processed 2D materials as CTLs, buffer layers, and additives in OSCs, coupled with the development of low-bandgap donors and NFAs, can be the key to unlock their spread in both large-scale and niche (*i.e.*, indoor) applications.

5. DSSCs

DSSCs are an intriguing alternative to the more conventional Si-based PV technology, owing to their potential low-cost



production and compatibility with flexible design.^{684–686} In a typical DSSC, a dye—sensitizing nanocrystalline TiO₂ on a TCO glass—absorbs the solar energy.^{52,687} The photoexcitation of the dye promotes electron injection toward the CB of nanocrystalline TiO₂.^{52,686} The electrons flow in the direction of the transparent electrode where they are collected for powering a load.^{52,686} After flowing through the external circuit, the electrons are reintroduced into the cell on a metal electrode on the back, called CE, where they are transferred to an electrolyte (also called the mediator).^{52,686} Then, the electrolyte transports the electrons back to the dye molecules.^{52,686} Thus, the original state of the dye is recovered. The mediator can be either an electrolyte containing a redox couple (such as I[−]/I₃[−]⁶⁸⁸ and Co²⁺/Co³⁺,⁶⁸⁹ for liquid-state DSSCs) or a HTL such as 2,2',7,7'-tetrakis[*N,N*-di(4-methoxyphenyl)amino]-9,9'-spirobifluorene (spiro-OMeTAD) for solid-state DSSCs.^{690–692}

The theoretical maximum V_{OC} value of a DSSC is regulated by the energy difference between the Fermi level of the metal oxide (typically TiO₂) semiconductor on the photoanode and the redox potential of the mediator.^{52,686} However, at a nonzero current, the output voltage is inferior to V_{OC} . In detail, the overall overpotential of the CE determines a voltage loss attributable to the delivery of current through the electrolyte/CE interface (kinetic overpotential or charge transfer overpotential) and through the electrolyte (mass transfer overpotential).⁶⁹³ The mass transfer overpotential is mainly affected by the ionic conductivity of the electrolyte and the transport of mediator species from the CE to the photoanode.^{694,695} Instead, the catalytic activity of the CE for the mediator reduction reaction defines the magnitude of charge transfer overpotential.^{693,694} Detailed descriptions of each component of a DSSC, as well as recent advances in DSSCs, can be found in several reviews.^{686,696,697}

To improve the performance and reducing the cost of DSSCs, the incorporation of new materials as well as the development of solution-processing techniques are actively pursued. In this context, GRMs have been extensively exploited in different DSSC components.^{698–702} In detail, they were first used as a transparent electrode to replace FTO at the photoanode.⁷⁰¹ Subsequently, they have been used as light absorbers,⁷⁰³ additives for improving charge transport through both TiO₂^{704–710} and electrolyte,^{711,712} and CE material for Pt replacement.^{699,713,714} Herein, we will overview the use of solution-processed GRMs in different components of DSSCs.

5.1 TCEs and photoanodes

TCEs, as well as entire photoanodes, are the key components in DSSCs. Traditionally, ITO ($R_s \sim 10\text{--}30 \Omega \square^{-1}$, T_r (550 nm) > 90%, $\phi_w \sim 4.8 \text{ eV}$)⁷¹⁵ and FTO ($R_s \sim 15\text{--}20 \Omega \square^{-1}$, $T_r \sim 85\%$ (300 < λ < 550 nm), $\phi_w \sim 4.4\text{--}5 \text{ eV}$)^{716–719} have been the most frequently used TCEs. However, ITO- and FTO-based electrodes have economic and technical issues, such as scarcity of In and high production/processing costs,⁷²⁰ as well as their crack susceptibility under tensile stress and structural defects.^{715,721} In this framework, pristine graphene and its derivatives promise to be ideal alternatives to traditional TCEs^{507,722} due to their high σ and T_r .⁷³ In particular, the preparation and processability

of GRMs, with controlled size,⁷²³ thickness,¹¹⁸ and chemical functionalities,¹¹⁹ by solution-based methods^{130,333} have provided simple and scalable ways to fabricate TCEs, compatible with high-throughput printing processes.^{333,724} In order to design DSSC photoanodes, several strategies have been pursued to minimize competition between light absorption, electron transport, and charge recombination processes: (i) the formulation of a composite of metal oxides with appropriate E_g to guarantee the ideal T_r value, allowing light to be effectively absorbed by the dye;^{725,726} (ii) the design of 1D metal oxides such as nanowires, nanorods, and nanotubes for (1) reducing the electron transport pathway (*i.e.*, increasing the electron diffusion coefficient (D_n)); (2) increasing the electron lifetime (τ) (*i.e.*, reducing the charge recombination losses);^{727–731} (iii) engineering 3D-metal-oxide-based light-trapping scaffolds for enhancing the light absorption, while reducing the photoanode thickness.^{732–734}

The first attempt to exploit graphene-based materials to replace conventional TCEs in DSSCs can be tracked back to the pioneering work of Wang *et al.*⁷⁰¹ The authors used transparent and conductive ultrathin (10 nm) graphene-based films, produced through graphite oxide exfoliation followed by a thermal reduction treatment.⁷⁰¹ However, poor PV performance was achieved as a consequence of both R_{series} and electronic interfacial changes introduced by defected edges in graphene platelets, which limited the hopping mechanism of electrons during their transport.^{735–739} Therefore, large graphene sheets are beneficial to reduce the number of boundaries and thus the contact resistances through the entire graphene film. These conclusions were very similar to those drawn in the field of OSCs. In the context of DSSCs, major efforts focusing on the incorporation of GRMs into DSSC photoanodes were aimed to form 2D bridges within mesoporous/nanostructured electrodes and to improve the electron collection efficiency.^{702,703,708,740–748} In fact, graphene and its derivatives can hold energy levels between those of photoanode metal oxide (typically TiO₂ or ZnO) CBs and ϕ_w of FTO (Fig. 11a).⁷⁴⁹ Consequently, graphene acts as an extended current collector (or electron transfer channel) for a rapid collection/transfer of the photogenerated electrons to the conductive substrate before the electrons recombine by interacting with the dye and/or the redox species (Fig. 11b).⁷⁵⁰ In addition, graphene insertion into photoanode metal oxides introduces hierarchical structures (*i.e.*, structures with a multiscale nanostructural ordering), which enhance light scattering.^{751,752} Thus, graphene effectively acts as light-capture centers to improve the overall η of DSSCs.^{747,753} Based on the aforementioned considerations, Yang and co-workers reported the use of TiO₂/graphene front electrode for enhancing DSSC η and J_{SC} by approximately 39% and 45%, respectively, compared to the reference DSSC using nanocrystalline TiO₂.⁷⁰³ Similar effects have also been reported by Gao and co-workers.⁷³⁹ In particular, Nafion (C₇HF₁₃O₅S-C₂F₄)-functionalized graphene dispersion and commercial TiO₂ NPs (P25) were used to prepare a graphene/TiO₂ nanocomposite-based TCE with a continuous 2D conductive network.⁷³⁹ The hydrophobic fluorine backbones of Nafion avoided the agglomeration of graphene flakes and conferred stability through electrostatic interactions between



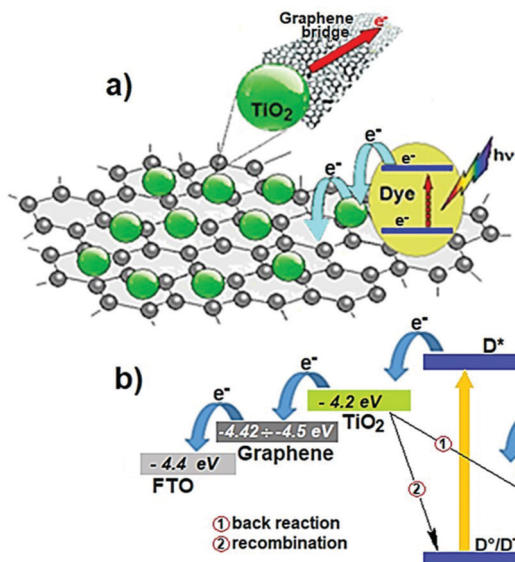


Fig. 11 (a) Schematic of light capture and electron transfer pathway from TiO₂ to the FTO, in TiO₂/graphene-based DSSC photoanodes. (b) Schematic of the electron cascade route in DSSC using TiO₂/graphene-based photoanodes.

the composite materials.⁷⁵⁴ It was proposed that this TCE morphology strongly influenced dye absorption, modulating the incident light harvesting, as well as the number of photo-induced electrons injected from the excited dye to the TiO₂ CB.⁷⁵³ Consequently, the DSSC incorporating 0.5 wt% graphene in the TiO₂ photoanode demonstrated an η value of 4.28%, which was 59% higher than that of the reference DSSC.⁷⁵³ Tsai *et al.* demonstrated that graphene-incorporated TiO₂ photoanode, prepared by spin coating, suppresses electron recombination, as well as enhances dye absorption onto the electrode surface.⁷⁵⁵ By using 1 wt% graphene, a 15% improvement in η (from 5.98% to 6.86%) was demonstrated.⁷⁵⁴

Xu *et al.* developed a highly conductive graphene scaffold incorporated into ZnO hierarchically structured NPs (HSN) capable of capturing and transporting photogenerated electrons.⁷⁵² The DSSCs, with a 1.2 wt% of graphene into the ZnO photoanode, exhibited an η value of $\sim 5.86\%$, higher than that of DSSCs without graphene.⁷⁵² Performance improvement due to graphene addition could be attributed to the combination of fast electron transport and long electron lifetime, which reduced the electron recombination losses (Fig. 12).⁷⁵²

Kusumawati *et al.* prepared a composite TiO₂/RGO porous photoanode in order to investigate the influence of RGO content (0.6, 1.2, and 3 wt%) on dye (N719) loading, as well as on the charge extraction transport properties of TiO₂ NPs.⁷⁴⁰ The authors found that RGO incorporation increased the film SSA, thereby promoting dye loading.⁷⁴⁰ This effect improved the light absorption, increasing J_{SC} and η (by $\sim 12\%$) as compared to those of the reference DSSC.⁷⁴⁰ The η enhancement was also ascribed to the optimized electron transport ($\sim 60\%$ increase in σ compared to bare TiO₂) in the TiO₂/RGO (1.2 wt%) composite photoelectrodes film.⁷⁴⁰ Hayashi *et al.* fabricated a multistep electron transfer system based on organic-inorganic ternary composites of Zn-porphyrin (ZnP), ZnO NPs, and RGO onto a FTO/SnO₂ electrode.⁷⁵⁶ The RGO flakes randomly distributed in the composite film acting as a 2D network, which assists the electron flow from ZnO-NP/ZnP composite to the FTO/SnO₂ electrode.⁷⁵⁵ This effect limited the charge recombination at the electrolyte interface and improved the photocurrent generation, resulting in an IPCE value of $\sim 70\%$ over the absorbed wavelength.⁷⁵⁵ The authors assessed that RGO can act as electron acceptor from ZnO-NP/ZnP composite, as well as a medium to store and shuttle electrons within the composite film.⁷⁵⁵ Fang *et al.* introduced different GO contents in TiO₂ NPs by ball milling and reported an η value of 5.09%, which was remarkably higher than that of the reference DSSC ($\eta = 4.43\%$).⁷⁵⁷ Sun and co-workers reported DSSCs based on graphene-TiO₂ composite photoanodes, achieving an η value of 4.28%, which was 59% higher than the

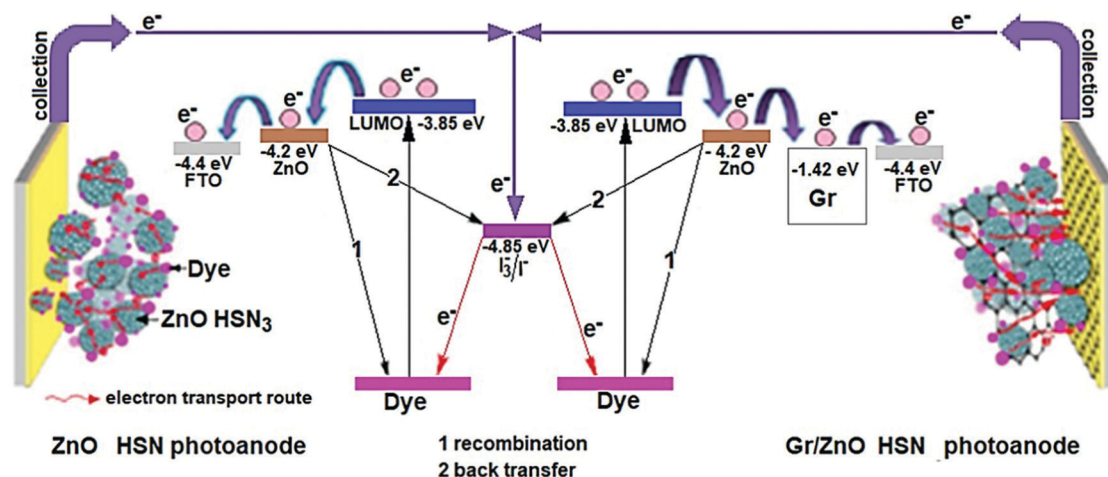


Fig. 12 Operating principle and energy diagram of the DSSC using ZnO HSN (left) or Gr/ZnO HSN (right). Electron injection from the excited dye into the nanostructured ZnO semiconductor, electron transport to the collection electrode, and the recombination (1) and back transfer (2) pathways are also shown. Reprinted with permission from ref. 752, Copyright 2013, American Chemical Society.



reference DSSC.⁷³⁹ It was found that the incorporation of graphene caused both increased dye adsorption and significantly longer electron lifetime compared to the graphene-free case.⁷³⁹ Chemically exfoliated graphene sheets (GS), incorporated by the grafting method in TiO₂ NP films, were synthesized by Tang *et al.* and used as the photoanode scaffold.⁷⁵⁸ Both high σ of reduced GS and optimum attachment of TiO₂ NPs on the GS were achieved by regulating the oxidation time during the chemical exfoliation process.⁷⁵⁷ Uniform films of GS/TiO₂ composite with large SSA were prepared on a conductive glass by electrophoretic deposition, and the integration of GS substantially increased the σ value of the film of TiO₂ NPs by more than two orders of magnitude.⁷⁵⁷ In addition, DSSCs based on GS/TiO₂ composite films reached η that is 5 times higher than that based on TiO₂ alone.⁷⁵⁷ The better PV performance of GS/TiO₂-based DSSC was also attributed to the higher dye loading of the GS/TiO₂ film compared to the GS-free case.⁷⁵⁷ Durantini *et al.* reported graphene-TiO₂ composite electrodes fabricated by hydrothermal synthesis or simple deposition by the spin-coating technique of TiO₂ paste onto a graphene layer.⁷⁰⁹ In both cases, no significant morphological differences were observed in the electrodes prepared with and without graphene.⁷⁰⁹ The DSSCs containing the graphene composite or layered films, enhanced both the J_{SC} (from 11.6 mA cm⁻² to 14.0 mA cm⁻²) and η (from 5.8% to 7.3%) values compared to the reference devices.⁷⁰⁹ Similar results have been reported by Chen *et al.* who developed a TiO₂/graphene/TiO₂ sandwich structure used as the photoactive layer in DSSCs, reaching η that was ~60% higher than the reference cell.⁷⁵⁹

It was speculated that electrons from the photoexcited dye are rapidly and efficiently transported to the CB of TiO₂ through the graphene-layer bridge, which both enhances the σ value of the photoelectrode and reduces charge recombination and back-reaction processes compared to the reference photoanode.⁷⁰³ In addition, the sandwich structure allowed light to be absorbed over a wide spectral range, enhancing the V_{OC} of DSSCs from 0.55 V to 0.6 V.⁷⁰³ Xiang *et al.* fabricated DSSCs based on TiO₂ photoanodes modified by GO and N-RGO, revealing better PV performance for N-RGO TiO₂ photoanode compared to the case based on GO.⁷⁶⁰ The DSSCs using N-RGO TiO₂ photoanode reached a 13.23% higher η compared to that of conventional TiO₂-based DSSCs.⁷⁵⁹ In particular, the V_{OC} value increased with N-RGO addition due to the suppression of electron recombination, while J_{SC} exhibited its maximum value at N-RGO content of 0.2 wt% owing to the synergistic effects of electron transfer efficiency, light scattering, and dye adsorption.⁷⁵⁹

Ding *et al.* produced RGO-TiO₂ composite films by mixing TiO₂ NPs with flakes of GO and ascorbic acid (vitamin C).⁷⁴² The latter enabled GO to be reduced at ambient temperature.⁷⁴² After treatment in a TiCl₄/H₂O solution followed by sintering at 450 °C, the RGO-TiO₂ NPs were sensitized by N719 dye and used as the photoanode in DSSCs.⁷⁴² The influence of RGO on the DSSC PV performances was evaluated at different RGO contents, varying from 0.25 to 0.75 wt%.⁷⁴² For a content of 0.75 wt%, the DSSCs reached the best PV performance with an η value of 7.89%, which was ~30% higher compared to that of its RGO-free device (6.06%).⁷⁴² This performance improvement

was attributed to the remarkable electric transport properties of RGO,⁷⁶¹ which captures and transports electrons, decreasing the overall charge recombination rate.⁷⁴² Notably, an excessive content of RGO (>0.75 wt%) caused the restacking of flakes, which were then ineffective in covering the TiO₂ NPs, eliminating their beneficial effects on the PV performance of DSSCs.⁷⁴² Mehmood *et al.* also studied the dependence of the η value of DSSC by GNP content in TiO₂/graphene composite-based DSSCs.⁷⁶² In particular, they fabricated photoanodes by adding GNPs into TiO₂ NP paste, obtaining the highest η of 4.03% with a GNP content of 0.16 wt%.⁷⁶¹ Higher GNP content negatively affected the DSSC performance.⁷⁶¹ This was attributed to the reduced T_r value of the TiO₂/graphene film, as well as to the presence of graphene aggregates inside the TiO₂ matrix, which can act as charge-trapping sites.⁷⁶¹ Sacco *et al.* investigated the charge transport and recombination properties in GO/TiO₂ composite-based DSSCs.⁷⁴¹ Impedance spectroscopy analysis revealed that GO incorporation into TiO₂ led to an increase in both D_n and τ , limiting the charge recombination processes and increasing the V_{OC} .^{739,763} He *et al.* designed and prepared a DSSC photoanode based on a RGO-TiO₂ heterostructure by cetyl-trimethylammonium-bromide (CTAB)-assisted hydrothermal method in order to wrap and anchor RGO with high-density TiO₂ NPs, resulting in a high-SSA (~83 cm² g⁻¹) composite.⁷⁶⁴ The inner RGO flakes ensured a rapid charge carrier transport route for effective charge collection at the conductive substrate, while the closely packed TiO₂ NPs limited direct contact between the RGO surface (rich in e⁻) and electrolyte (rich in h⁺), preventing charge recombination processes.⁷⁶³ Because of these multiple effects, DSSCs based on RGO have shown an η value enhancement of ~40% compared to the reference one.⁷⁶³ Ranganathan *et al.* exploited N-doped graphene@nickel oxide (NG/NiO) nanocomposite-doped TiO₂, deposited onto FTO substrates by screen printing, as the photoanode.⁷⁶⁵ The corresponding DSSCs have shown η up to 9.75%, which was higher than those of DSSCs using GO/TiO₂-, TiO₂-, and NiO/TiO₂-based photoanodes (8.55, 8.69, and 9.11%, respectively).⁷⁶⁴

Graphene was also used in QD-based DSSCs (QDDSSCs),⁷⁶⁶ also named QD-sensitized solar cells (QDSSCs) (see additional discussion in Section 6), to realize graphene-TiO₂ hybrid photoanodes. For example, Zu *et al.* fabricated CdS-QDDSSCs based on a graphene-TiO₂ film photoanode (0.8 wt% of graphene), improving the η value by ~55% compared to a reference DSSC with a pristine TiO₂-based photoanode.⁷⁶⁷

Yan *et al.* synthesized—*via* stepwise solution chemistry—large, soluble graphene QDs with 1,3,5-trialkyl-substituted phenyl moieties covalently attached at the edge of graphene QDs and used as sensitizers in DSSCs.⁷⁰² However, despite the higher molar extinction coefficient (κ) (~1 × 10⁵ M⁻¹ cm⁻¹) of GQDs compared to that of N719 dye (~1.5 × 10⁴ M⁻¹ cm⁻¹),⁷⁰² the fabricated QDDSSC exhibited suitable V_{OC} (0.58) and FF (0.48 V) values, but small J_{SC} (0.2 mA cm⁻²) due to low affinity between GQDs and TiO₂ surface.⁷⁰² Subsequently, the incorporation of both 3D graphene structure and GSs into TiO₂ was evaluated to clarify their influence on charge transport through the graphene/TiO₂ interface in QDDSSCs using CdS/CsSe QDs.⁷⁶⁸ From the *I*-*V*





Fig. 13 (a) Schematic of the energy-level diagram and electron transfer process in P1-graphene-based DSSCs. (b) J - V curves and IPCE spectra for DSSCs with and without a P1-G layer. Adapted with data from ref. 769.

curve analysis, as a function of GQD content in photoanode formulation, it was observed that η and J_{SC} reached the maximum value at a graphene content of 1.5 wt%, and then decreasing at higher contents.⁷⁶⁷ On the contrary, both FF and V_{OC} have shown no correlation with the GQD concentration.⁷⁶⁷ These features highlighted the strong correlation between J_{SC} and η ^{739,741,766,767} with graphene content, while it was suggested that the composite semiconductor E_F ⁵² and device series resistance⁷⁶⁹ are not affected by the incorporation of graphene.

In a recent work, a novel approach based on graphene has been used to fabricate a DSSC with an η value of 10.4%, representing an $\sim 28\%$ improvement compared to the reference cell based on conventional TiO₂-based photoanodes ($\eta = 7.5\%$).⁷⁷⁰ In detail, graphene dispersed in *o*-dichlorobenzene was uniformly incorporated in a semiconducting polymer with commensurate band edges (P1) (see chemical structure in ref. 771) and the resulting composite (P1-graphene) solution was spin coated over the cell photoanode to act as a barrier layer limiting the back-transfer process of electrons (Fig. 13).⁷⁶⁹ At a graphene concentration of 0.9 wt%, experimental data proved the favorable influence of the P1-G barrier layer in improving the dye regeneration ability.⁷⁶⁹ In detail, graphene effectively acts as a scavenger for electrons at P1, directing the electrons to the HOMO of the dye for the regeneration process.⁷⁶⁹ The P1-G-based device has shown higher recombination resistance (R_{rec}) compared to that of the reference device.⁷⁶⁹ In addition, P1-G-based device displayed a τ value of 113 ms at the photoanode, more than double that of the reference device (*i.e.*, 45 ms).⁷⁶⁹ Finally, cyclic voltammetry (CV) and photoluminescence measurements revealed that the use of P1-G resulted in charge injection from the redox electrolyte to the HOMO level of the dye that was higher than that exhibited by the standard device (TiO₂ surface). Moreover, the addition of graphene in P1 decreased the photoluminescence intensity from 9.3×10^4 in the P1 film to 5.2×10^4 counts in P1-G films. This last feature further testified that graphene acts as a scavenger for electrons at P1, leading the electrons to the HOMO of the dye for the regeneration process.

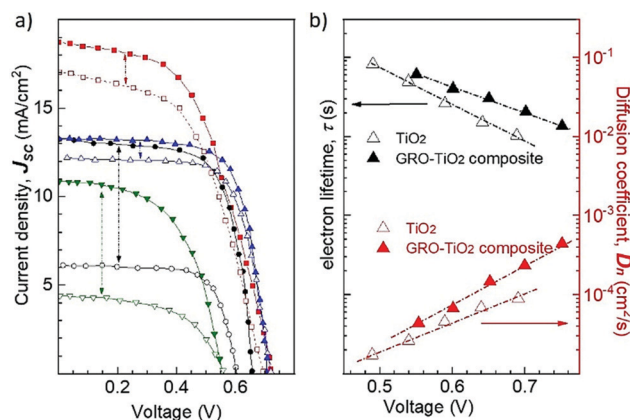


Fig. 14 (a) Typical J - V curves of DSSCs based on different GRM-based photoactive layers (line and full symbols) compared to those of the corresponding traditional TiO₂-based photoelectrode. (b) Electron diffusion coefficient (D_n) and lifetime (τ) dependence on the applied voltage for DSSCs based on TiO₂ photoactive layers with and without GRMs. Adapted from ref. 741,742,758,759.

Fig. 14 summarizes the J - V curves of representative DSSCs using TiO₂-GRMs composite-based photoanodes, compared to those of the equivalent TiO₂-based cells, and the corresponding D_n and τ data.

Table 6 lists the experimental results achieved in DSSCs using solution-processed GRMs as the photoanode material. For each case, the η value is compared with that of the TiO₂-based photoanode reference.

5.2 CEs

5.2.1 Graphene and graphene derivatives. In DSSCs, the CE collects the photogenerated electrons from the external circuit and catalyzes the oxidized electrolyte regeneration.⁵² The reduction in the overall overpotential of CE (*i.e.*, decrease of R_{CT}), attributable to the delivery of current through the electrolyte/CE interface, is crucial for limiting the voltage loss within the DSSCs.⁵² An effective CE should have high σ and exhibit high electrocatalytic activity toward the mediator



Table 6 Summary of the PV performance of DSSCs using 2D material-based photoanodes

Photoanode structure	Dye	Cell performance					Ref.
		J_{SC} (mA cm ⁻²)	V_{OC} (V)	FF (%)	η (%)	$\Delta\eta$ (%)	
TiO ₂	N3	11.26	0.69	64.5	5.01	39.1	703
TiO ₂ /GO (0.6 wt%)		16.29	0.69	62.0	6.97		
TiO ₂	N719	18.83	0.684	46.48	5.98	14.7	754
TiO ₂ /graphene (1 wt%)		19.92	0.704	48.86	6.86		
TiO ₂	N719	11.0	0.71	74.1	5.78	29.6	740
TiO ₂ /graphene (1.2 wt%)		14.4	0.68	76.80	7.49		
TiO ₂ nanofibers	N719	13.9	0.71	63	6.3	20.6	772
TiO ₂ nanofibers/graphene (0.7 wt%)		16.2	0.71	66	7.6		
TiO ₂	N719	8.69	0.77	66	4.42	36.9	773
TiO ₂ /graphene (1.0 wt %)		12.89	0.68	69	6.05		
TiO ₂	N3	8.787	0.606	65.97	4.43	14.9	756
TiO ₂ /GO		10.284	0.616	63.75	5.09		
TiO ₂	N3	9.58	0.82	62	4.89	32.7	707
TiO ₂ /graphene (0.5 wt%)		12.78	0.82	62	6.49		
TiO ₂	N719	10.99	0.68	71.3	5.3	34	774
TiO ₂ /graphene (0.2 wt%)		13.93	0.70	73.4	7.1		
TiO ₂	N719	13.2	0.691	52.4	4.78	60.1	775
TiO ₂ /RGO (1.6 wt%)		18.39	0.682	61.2	7.68		
TiO ₂	N719	10.75	0.686	56.6	4.2	31.0	776
TiO ₂ /RGO (0.75 wt%)		12.16	0.668	67.7	5.5		
TiO ₂	N719	6.18	0.606	71	2.67	110.5	741
TiO ₂ /RGO (0.25 wt%)		13.04	0.645	67	5.62		
TiO ₂	N719	12.5	0.669	66.0	5.52	17.6	777
TiO ₂ /graphene (0.5 wt%)		13.7	0.685	69.2	6.49		
TiO ₂	N719	16.13	0.62	65.3	6.57		778
N-Doped TiO ₂		16.71	0.74	61.6	7.64	16.3	
N-Doped TiO ₂ /GO (0.1 wt%)		19.65	0.74	64.70	9.32	41.9	
TiO ₂	N719	10.30	0.64	73	4.81	29.3	779
TiO ₂ /GQDs		11.72	0.68	78	6.22		
TiO ₂	N719	12.59	0.704	65.07	5.77		780
TiO ₂ /RGO (0.6 wt%)		14.52	0.697	68.22	6.91	19.8	
TiO ₂ /graphene sheets (0.6 wt%)		17.31	0.690	69.04	8.24	42.8	
Pristine TiO ₂	N719	11.1	0.693	67.7	5.21	45.1	781
TiO ₂ /graphene (0.03 wt%)		16.5	0.703	65.2	7.56		
TiO ₂	N719	10.7	0.75	76.82	6.13	11.7	782
TiO ₂ RGO (3.12 wt%)		12.9	0.76	69.20	6.85		
TiO ₂ nanotubes (TT)	N719	9.19	0.71	61.3	4.00	33.3	783
TT/RGO (2 wt%)		10.7	0.78	63.9	5.33		
TiO ₂	N719	15.5	0.71	0.68	7.51	38.9	769
TiO ₂ /P1-graphene		19.8	0.74	0.71	10.43		
TiO ₂	N719	17.46	0.75	0.66	8.69		764
TiO ₂ /GO		16.70	0.74	0.68	8.55	-1.6	
TiO ₂ /NiO/NGE		19.04	0.76	0.67	9.75	12.2	
TiO ₂	N719	11.51	0.72	0.66	5.52	37.1	784
TiO ₂ /RGO		16.75	0.74	0.65	7.57		
ZnO	N719	3.0	0.45	—	3.7	76.2	785
ZnO/B-doped GQDs		7.5	0.43	—	2.1		
TiO ₂	N719	9.30	0.68	0.48	3.0	173.3	786
TiO ₂ /graphene		27.49	0.67	0.45	8.2		
TiO ₂ nanofibers	N719	14.0	0.73	0.72	7.3	21.9	787
TiO ₂ nanofibers/graphene		18.0	0.73	0.68	8.9		
TiO ₂	N719	13.3	0.82	0.58	6.32	36.4	788
TiO ₂ /RGO		20.6	0.79	0.53	8.62		
TiO ₂	Mimosa pudica				0.059	69.5	789
TiO ₂ /RGO		16.085	0.248	—	0.1		
SnO ₂ :TiO ₂	N719	7.76	0.67	0.56	2.91	15.8	790
Graphene-doped SnO ₂ :TiO ₂		9.03	0.65	0.58	3.37		
MoS ₂	N719	9.32	0.67	0.52	3.36	165	791
MoS ₂ /graphene nanocomposite		15.82	0.82	0.71	8.92		

reduction reaction. For the case of liquid-state DSSCs, the reduction reaction involves the redox couple I^-/I_3^- and is $I_3^- + 2e^- \rightarrow 3I^-$. Thus, in order to minimize the charge transfer overpotential, high σ for charge transport and electrocatalytic activity for reducing the redox couple, as well as electrochemical stability, are fundamental requirements for CE materials.⁷⁹²

Noble metals, (e.g., Pt, Au, and Ag) have been largely used as CE materials, with Pt representing the most popular one.⁷⁹³ However, noble metals are expensive and their corrosion in DSSC liquid electrolytes is a critical shortcoming that hinders the commercialization of DSSC technology. Therefore, research activities have been focused on the development of metal-free



CEs for low-cost DSSCs. In this framework, carbon-based materials (e.g., CNTs,^{794–796} GNPs,^{713,797–799} functionalized graphene sheets (FGSs),⁷¹² hybrid structures, GNPs/RGO/CNT,^{700,800} graphene/SWNT composite,⁸⁰¹ and N-doped GNPs (NGNPs)^{802,803}) and scalable solution-based processes for electrode fabrication methods (e.g., spin coating,⁸⁰⁴ flexographic printing,⁷⁹⁸ electrophoretic deposition (EpD)⁸⁰⁵) have been developed and exploited with the aim to replace traditional, expensive Pt-based CEs. Graphene-based materials have been used as the CE in the DSSC ambience since 2008⁸⁰⁶ and some investigations have shown that combinations of two carbon materials (e.g., CNTs/graphene⁸⁰⁷ or porous carbon/CNTs⁸⁰⁸) can enhance the electrochemical activity of CEs. In particular, CE based on micrometer-thick graphene films can show R_{CT} approaching to those of Pt-based CEs, which can even be inferior to $1 \Omega \text{ cm}^2$ for the reduction of I_3^- .^{809–811} For example, Kaniyoor and Ramaprabhu used thermally exfoliated graphene (TEGr) as a novel electrocatalyst material for I_3^- reduction.⁸¹² Their TEGr-based CE has shown a R_{CT} of $\sim 11.7 \Omega \text{ cm}^2$ that, although higher than that of their Pt-based CE ($\sim 6.5 \Omega \text{ cm}^2$), was lower than that reported for graphite-based CE.⁸¹³ Counter electrodes based on thin-film GRMs have been demonstrated to be extremely effective for DSSCs using mediators different than traditional I^-/I_3^- , particularly the $\text{Co}(\text{bpy})_3^{2+/3+}$ redox couple.⁶⁹⁷ For example, thermally reduced graphene oxide (TRGO)-based CEs allow flexible DSSCs to be realized with an η value of $\sim 5\%$, comparable to that obtained using platinized FTO (5.5%), suggesting that the functional groups and defects of graphene can play an important role in catalysis.⁷¹² More recently, a printable graphene-based ink obtained by the LPE of graphite has been spray-coated onto a TCO substrate to replace Pt in a large area ($\geq 90 \text{ cm}^2$) semitransparent ($T_r = 44\%$) CE.⁴⁰⁵ A large-area DSSC module (43.2 cm^2 active area) using the constructed CE achieved an η value of 3.5%, V_{OC} of 711 mV, J_{SC} of 14.8 mA cm^{-2} , and FF of 34.7%.⁴⁰⁵ Yen *et al.*⁸¹⁴ prepared a composite dispersion of graphene/metal NPs *via* the $\text{H}_2\text{O}/(\text{CH}_2\text{OH})_2$ synthesis method.⁸¹⁵ Then, they fabricated a graphene/Pt NP-based CE on the FTO substrate.⁸¹³ The Pt incorporation improved the graphene reduction degree, and the composite materials synergistically enhanced the electrocatalytic properties of the CE.⁸¹³ The DSSC based on the as-produced CE afforded an η value of 6.35% (J_{SC} of $\sim 12 \text{ mA cm}^{-2}$, V_{OC} of $\sim 0.8 \text{ V}$, and FF of ~ 0.7), which is $\sim 20\%$ higher compared to the reference DSSCs.⁸¹³ Ju and co-workers developed heteroatom-doped graphene nanomaterials for DSSC CEs.⁸⁰¹ In detail, they used N-doped GNPs, deposited onto FTO/glass substrates through electrospray coating, as the CEs in a DSSC using a $\text{Co}(\text{bpy})_3^{3+/2+}$ redox couple and JK225 organic dye sensitizer containing bis-dimethylfluorenyl amino group as the electron donor and cyanoacrylic acid as the electron acceptor and bridged by an indeno[1,2-*b*]thiophene unit.⁸¹⁶ N-doping induced a structural deformation in the hexagonal lattice of the graphene layer of the GNPs *via* local strains, as well as produced additional electron/ion pair with electrocatalytic activity.^{817,818} Therefore, the DSSCs based on N-GNP CE reached an η value of 9.05%, which outperformed that obtained using Pt-based CE (8.43%).⁸⁰¹ By means of N-GNP CE, the measured R_{CT}

($1.73 \Omega \text{ cm}^2$) was significantly lower than that obtained with Pt-based CE ($3.15 \Omega \text{ cm}^2$).⁸⁰¹

Functionalized graphene sheets (FGSs), containing lattice defects and oxygen functional groups (e.g., OH, C=O, and epoxides), were thermally treated at a temperature of 1000–1500 °C to heal the lattice defects and tune the C/O ratio and used as the CEs.⁷¹² FGS-based inks were directly cast on a nonconductive plastic substrate without the need of a conductive substrate.⁷¹² The corresponding DSSCs based on FGS/surfactant/polymer network produced *via* the thermolysis process displayed an η value of 4.99%, which was close to that of Pt-based DSSCs (5.48%).⁷¹² Electrochemical impedance spectroscopy (EIS) and CV measurements suggested that R_{CT} increases with decreasing O-containing functional groups, lowering the PV performance.⁷¹² Therefore, CE with C/O ratio of < 7 was not sufficiently conductive for use as a CE material.⁷¹²

In addition, it was proved that a low C/O ratio gives rise to a coarse film structure because of increased agglomeration.⁷¹² All these results proved that the optimization of functionalization/morphology is crucial to control the R_{CT} , realizing low-cost and flexible CEs. By applying graphene-based CEs (namely, GNP-based CEs) to the most advanced DSSC configurations, Kakiage *et al.* reached the current record η value for DSSCs, *i.e.*, 14.7%.⁸³⁰ Noteworthily, the previous record η of 13.0% was also achieved using graphene-based CEs.⁸³¹

Table 7 summarizes the PV parameters of selected DSSC configurations using solution-processed graphene-based CEs.

5.2.2 Two-dimensional TMDs. Among the GRMs, TMDs such as MoS_2 , MoSe_2 , WS_2 , and WSe_2 have been the most studied 2D materials to be used as CEs for low-cost Pt-free DSSCs.^{832,833} Wu *et al.* proposed MoS_2 and WS_2 as the CE materials in I_3^-/I^- , T_2/T^- , and S_2/S^- -based DSSCs.⁸³⁴ CV measurements revealed that both MoS_2 - and WS_2 -based CEs hold a catalytic activity, for the redox couple regeneration, comparable to that of the Pt-based CE.⁸³³ Consequently, the DSSCs using MoS_2 - and WS_2 -based CEs have shown an η value of 7.59% and 7.73%, respectively, which were comparable to that of the reference DSSC using a Pt-based CE.⁸³³ EIS analysis estimated R_{CT} values of 0.5 and 0.3Ω for MoS_2 - and WS_2 -based CE, respectively, together with large electrode capacitances (134 and $198 \mu\text{F}$, respectively) (*i.e.*, large SSA).⁸³³ These values outperformed those of Pt-based CE (R_{CT} of 3Ω and capacitance of $2.1 \mu\text{F}$).⁸³³

Freitas *et al.* prepared MoS_2 through a hydrothermal route to be used as the CE material using I^-/I_3^- as the redox couple.⁸³⁵ MoS_2 -based DSSCs reached an η value of 2.9%, while DSSCs based on Pt CE has shown $\eta = 5.2\%$.⁸³⁴ Although the η value of MoS_2 -based DSSCs was lower than that of Pt-based DSSCs, the possibility to dry MoS_2 -based CE at a temperature of 120 °C was considered to be an advantage for the manufacturing of low-cost Pt-free DSSCs.⁸³⁴ Next, Al-Mamun *et al.* grew ultrathin MoS_2 -nanostructured films onto the FTO substrate through a facile one-pot hydrothermal method.⁸³⁶ It was demonstrated that the temperature of the hydrothermal reaction and the molar ratio of reaction precursors have a relevant effect on the structure of the resulting MoS_2 .⁸³⁵ An ultrathin MoS_2 film



Table 7 Summary of the PV performance of DSSCs using graphene-based CEs

Materials	Device structure	Cell performance					Ref.
		R_{CT} ($\Omega\text{ cm}^2$)	J_{SC} (mA cm^2)	V_{OC} (V)	FF (%)	η (%)	
Graphene	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /graphene	38.0	14.3	0.54	0.653	5.69	819
TiN/graphene	FTO/TiO ₂ /dye/I ⁻ /I ₃ ⁻ /TiN-graphene	5.67	12.34	0.73	0.643	5.78	802
Pt/graphene	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /Pt-graphene	0.67	12.06	0.79	0.67	6.35	813
GNPs	FTO/TiO ₂ /Y123/Co ^{2+/3+} /GNPs	0.70	12.70	1.03	0.70	9.30	796
Pt-RGO	FTO/TiO ₂ /dye/I ⁻ /I ₃ ⁻ /Pt-RGO	—	14.10	0.72	0.67	6.77	820
GNSs/AC	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /GNSs-AC	0.5 ÷ 0.8	13.30	0.76	0.738	7.50	821
NGNPs	FTO/TiO ₂ /dye/Co(III/II)/NGNPs	1.73	13.83	0.883	0.742	9.05	801
GNTs/graphene-Rib	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /GNT/graphene-Rib	—	16.73	0.730	0.670	8.23	806
GQD-PPy	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /GQD-doped PPy	—	14.36	0.723	0.580	5.27	822
Au/GNP	FTO/TiO ₂ /ADEKA-1/LEG4/Co ^{2+/3+} /Au/GNP	—	19.55	0.995	0.776	14.7	829
NGNPs	FTO/TiO ₂ /YD2-o-C8/Co ^{2+/3+} /NGNPs	0.45	13.33	0.870	0.720	8.30	823
aGNP	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /aGNP	2.68	22.54	0.73	0.47	7.7	824
Pt/GONF	FTO/TiO ₂ /Y123/Cu ⁺ /Cu ⁺ /Pt/GONF	1.1	14.01	1.02	0.665	9.5	825
PEDOT/RGO	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /PEDOT-RGO	18.17	15.82	0.73	0.67	7.79	826
3D graphene networks/RGO	FTO/TiO ₂ /RGO/N719/I ⁻ /I ₃ ⁻ /3D graphene networks/RGO	9.61	21.0	0.75	0.661	9.79	827
RGO QDs	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /RGO QDs	64.8	6.1	0.784	0.52	2.5	828
GO	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /GO	52.26	11.83	0.66	0.715	5.6	829
CVD graphene/FLG	FTO/TiO ₂ /Y123/Co ^{2+/3+} /FLG/CVD graphene	—	11.23	0.958	0.47	5.09	406
GNPs	FTO/TiO ₂ /SM315Co(bpy) ₃ ^{12+/3+} /GNPs	—	18.1	0.91	0.78	13.0	830

was obtained through a hydrothermal process with a reaction solution comprising NH₂CSNH₂ and (NH₄)₆Mo₇O₂₄·4H₂O with a molar ratio of 28 : 1 at 150 °C for 24 h.⁸³⁵ After calcination at 400 °C in Ar, the resulting MoS₂ films were used as CEs for DSSCs, reaching an η value of 7.41%.⁸³⁵ This value was superior to that measured for Pt-based DSSCs (7.13%).⁸³⁵ Meanwhile, homogeneous CNTs-MoS₂-C with ultrathin, uniform lamellar structure of MoS₂ was synthesized by Liu *et al.* via wet impregnation and calcination method.⁸³⁷ This work indicated that the addition of a nonionic surfactant (PEG400) promotes the dispersion of (NH₄)₂MoS₄ onto the surface of CNTs, inhibiting the formation of independent particles of MoS₂. The DSSCs using CNTs-MoS₂-C composite-based CE achieved an η value of 7.23%, which was higher than that of Pt-based DSSCs (6.19%). Yue *et al.* synthesized flower-like structure complexes of MoS₂/SWCNTs with glucose and PEDOT:PSS-assisted *in situ* hydrothermal route.⁸³⁸

Dye-sensitized solar cells based on MoS₂/SWCNTs as the CE exhibited an η value of 8.14%, superior to that of Pt-based DSSCs (7.78%).⁸³⁷ Kim *et al.* used atomically thin 2D MoS₂ nanoflakes, produced by a simple intercalation/exfoliation process, for fabricating transparent CEs *via* spin coating of the MoS₂ dispersion followed by thermal treatment.⁸³⁹ The authors found that DSSCs based on MoS₂ thermally treated at 100 °C exhibited an η value of 7.35%, which was comparable to that of the reference one, *i.e.*, Pt-based DSSC (η = 7.53%).^{838,840} Solution-processed mesoporous WO₃ films with 3D, rough, and high-curvature surfaces followed by a rapid sulfurization process to prepare an edge-oriented WS₂ thin film was presented (Fig. 15). The maximized active edge sites on the high-curvature surface and electron transfer *via* continuous WS₂ building blocks enhanced the catalytic activity toward the I₃⁻ reduction reaction in WS₂-based CEs.⁸³⁹ This feature allowed WS₂-based DSSCs to reach an η value of 8.85%, *i.e.*, superior to that of the Pt-based

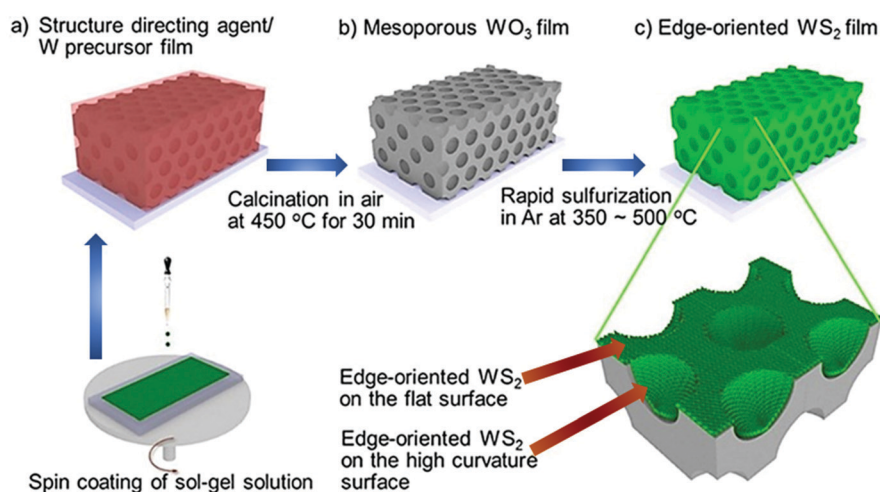


Fig. 15 Schematic of the preparation of solution-processed mesoporous WO₃ thin film and its conversion to edge-oriented WS₂ thin film. Adapted from ref. 839.



reference (7.20%).⁸³⁹ More recently, Vikraman *et al.* proposed a synthesis route to fabricate MoS₂/FTO CE *via* a simple chemical bath (pH \approx 10) deposition process by means of thiourea (CH₄N₂S, 0.5 M) as the sulfur source and ammonium-heptamolybdate-tetrahydrate ((NH₄)₆Mo₇O₂₄·4H₂O, 0.01–0.03 M), followed by annealing (450 °C for 60') in a S environment to obtain crystalline MoS₂.⁸⁴¹ Under these conditions, the following reactions have been suggested: (1) CH₄N₂S + 2H₂O \rightarrow CO₂[↑] + 2NH₃[↑] + H₂S[↑]; (2) (NH₄)₆Mo₇O₂₄·4H₂O + 28H₂S + 8NH₃ \rightarrow 7(NH₄)₂MoS₄ + 28H₂O; (3) (NH₄)₂MoS₄ + 2N₂H₄ \rightarrow MoS₂ + N₂[↑] + 2(NH₄)₂S.⁸⁴⁰

Raman spectroscopy, XPS, and scanning electron microscopy (SEM) analyses evidenced the presence of tri- and tetra-layered MoS₂ and agglomeration effects, depending on the molybdate concentration and deposition time, respectively.⁸⁴⁰ Mo precursor concentration of 0.01 M and bath temperature and deposition time of 90 °C and 5', respectively, led to the optimal morphology of MoS₂ layers with spherical-shaped grains and absence of agglomeration effects.⁸⁴⁰ In addition, agglomerations of uniform spherical grains provide large SSA with numerous edge sites, thereby promoting the electrocatalytic activity.⁸⁴⁰ In this context, a deposition time of 30 min resulted in the optimal performance of DSSCs using the MoS₂/FTO CE.⁸⁴⁰ Under longer deposition times (\sim 45 min), MoS₂ changed from the layered to bulk structure, showing a phase transformation from MoS₂ to Mo₂S₃.⁸⁴⁰ These effects lowered the catalytic activity of the CE due to the presence of an insufficient number of sulfur active sites in the material structure.⁸⁴⁰ In addition, MoS₂/FTO CE has shown an electrocatalytic activity toward I₃[−] reduction, corresponding to R_{CT} (\sim 8.3 Ω cm^{−2}) comparable to that of Pt/FTO (\sim 7.2 Ω cm^{−2}).⁸⁴⁰ The PV performance of optimized MoS₂/FTO-based DSSCs (J_{SC} = 15.92 mA cm^{−2}, V_{OC} = 0.73 V, FF = 0.61, and η = 7.14%) almost reached that of the reference one based on Pt/FTO CE (J_{SC} = 17.84 mA cm^{−2}, V_{OC} = 0.71 V, FF = 0.69, and η = 8.73%).⁸⁴⁰ Fig. 16 compares the J - V curves of the MoS₂/FTO and Pt/FTO CE-based DSSCs under the same illumination conditions.⁸⁴⁰ The anodic and cathodic branches of the Tafel polarization curves (Fig. 16, inset) indicate that the catalytic activity of MoS₂/FTO

and Pt/FTO CEs is comparable.⁸⁴⁰ In fact, larger the slope in the anodic/cathodic branch, higher are the exchange current densities on the electrode, which then shows higher electrocatalytic activity and lower R_{CT} at the electrolyte/CE interface (see eqn (3.5)).⁸⁴²

Recently, MoSe₂/WS₂ heterostructures on FTO have been proposed as the DSSC anode, providing a simple route to optimize interfacial transport for enhancing the electrocatalytic properties of DSSC anodes. By optimizing the thickness of the WS₂ layer, a maximum η value of 9.92% was reached, proving the potential of combining TMDs in advanced functional structured anodes.⁸⁴³

Table 8 summarizes the PV performance obtained in DSSCs using solution-processed TMD-based CEs.

5.2.3 Two-dimensional material-based hybrids. The hybridization of different materials is, in principle, an effective method to produce advanced CE composites with enhanced synergistic electrocatalytic activity in comparison to the single counterparts. In fact, Wen *et al.* developed a metal-nitride/graphene nanohybrid (*i.e.*, TiN-decorated N-doped graphene) to be used as a CE material for DSSCs.⁸⁰² The latter exhibited higher η (5.78%) than that of the Pt-based reference (5.03%), demonstrating the potential role of these hybrid structures to replace Pt-based CEs, with the added value of cost reduction and easy cell fabrication.⁸⁰² Tjoa and co-workers developed a low-temperature route to synthesize hybrid GO/Pt NP composites by light-assisted spontaneous co-reduction of GO and chloroplatinic acid.⁸¹⁹ The hybrid composites were used as CE materials in DSSCs, achieving an η value of 6.77%, which was higher than that of Pt-based references (6.29%).⁸¹⁹ In addition, the hybrid materials were compatible with flexible plastic substrates, yielding flexible DSSCs with an η value of 4.05%.⁸¹⁹ Lin *et al.* produced hybrid MoS₂/GNS through EpD onto a FTO substrate to be used as the CE material in DSSCs.⁸⁴⁴ The resulting DSSCs achieved an η value of 5.81% and low R_{CT} (2.34 Ω cm²), which was the result of a synergic effect derived by the combination of the single material components.⁸⁴³ In fact, DSSCs using only GNS or MoS₂ as the CE exhibited poor η (4.68% and 4.15%, respectively) and higher R_{CT} (6.24 and 3.65 Ω cm², respectively), testifying the occurrence of synergistic catalytic effects in the hybrids.⁸⁴³ MoS₂/graphene hybrid as the CE for DSSCs have also been reported by Yue *et al.* showing performance comparable to that of Pt CE.⁸⁴⁵ The hybrid electrodes were more efficient than those based on MoS₂, with MoS₂/graphene-based DSSCs reaching an η value of 5.98%, which was similar to that of the Pt-based reference (6.23%).⁸⁴⁴

Liu *et al.* also reported MoS₂/graphene hybrid as the CE material.⁸⁶⁴ The hybrids were synthesized by mixing GO nano-sheets with ammonium tetrathiomolybdate and converting the solid intermediate into MoS₂/RGO hybrid by flowing H₂ at 650 °C.⁸⁶³ The DSSCs using MoS₂/RGO hybrid CE have shown excellent electrocatalytic activity toward I₃[−] reduction, together with optimal electrochemical stability.⁸⁶³ CV and EIS measurements evidenced the superior electrocatalytic activity and lower R_{CT} (0.57 Ω cm²) of the MoS₂/RGO-based CE compared to the CEs based on RGO, MoS₂, and sputtered Pt.⁸⁶³ The DSSCs assembled

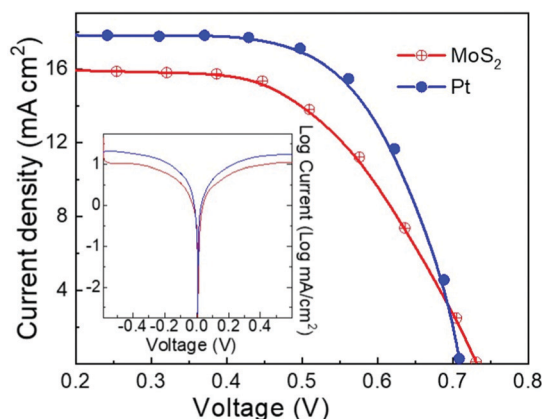


Fig. 16 J - V curves of DSSCs with MoS₂/FTO and Pt/FTO CEs. Inset shows the Tafel polarization curves of symmetrical cells with MoS₂/FTO and Pt/FTO CEs. Adapted from ref. 840.



Table 8 Summary of the PV performance of DSSCs using TMD-based CEs

Material	Device structure	Cell performance					Ref.
		R_{CT} ($\Omega \text{ cm}^2$)	J_{SC} (mA cm^{-2})	V_{OC} (V)	FF (–)	η (%)	
MoS ₂ catalyst	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoS ₂ /FTO	0.50	13.84	0.76	0.73	7.59	833
WS ₂ catalyst	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /WS ₂ /FTO	0.30	14.13	0.78	0.70	7.73	833
Carbon-coated WS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /WS ₂ /FTO	5.0	13.10	0.67	0.62	5.5	846
NbSe ₂ nanorods	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /NbSe ₂ /FTO	6.21	13.94	0.76	0.64	6.78	846
NbSe ₂ nanosheets	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /NbSe ₂ /FTO	2.59	15.04	0.77	0.63	7.34	847
NbSe ₂ nanosheets	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /NbSe ₂ /FTO	—	16.85	0.74	0.62	7.73	848
NbSe ₂ nanorods	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /NbSe ₂ /FTO	—	14.85	0.74	0.46	5.05	847
NbSe ₂ nanoparticles	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /NbSe ₂ /FTO	—	14.93	0.75	0.55	6.27	847
Porous MoS ₂ sheets	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoS ₂ /FTO	1.73	15.40	0.763	0.53	6.35	849
MoS ₂ nanoparticles	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoS ₂ /FTO	93.0	14.72	0.745	0.490	5.41	850
MoS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoS ₂ /FTO	18.50	18.46	0.680	0.580	7.01	851
MoS ₂ nanosheets	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoS ₂ /FTO	0.619	18.37	0.698	0.578	7.41	835
MoSe ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoSe ₂ /FTO	229.8	13.0	0.67	0.68	5.90	852
NiS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /NiS ₂	50.40	14.70	0.72	0.52	5.50	851
NiSe ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /NiSe ₂	45.00	14.30	0.75	0.68	7.30	851
CoSe ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /CoSe ₂	10.70	13.50	0.72	0.68	6.60	851
MoSe ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoSe ₂	2.43	14.11	0.73	0.65	6.70	853
WSe ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /WSe ₂	0.78	15.50	0.73	0.66	7.48	852
TaSe ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /TaSe ₂	1.89	15.81	0.73	0.64	7.32	852
MoS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoS ₂ /FTO	30.98	16.90	0.727	0.517	6.35	854
MoS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /1 T-MoS ₂ /FTO	19.0	8.76	0.730	0.520	7.08	855
MoS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoS ₂ /FTO	15.29	14.94	0.718	0.67	7.19	856
MoS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoS ₂ /FTO	12.9	16.96	0.74	0.66	8.28	857
MoS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /1T-MoS ₂ /FTO	19.60	11.54	0.80	0.65	6.0	858
TiS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /TiS ₂ /FTO	0.63	17.48	0.73	0.603	7.66	859
MoS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoS ₂ /graphite paper	2.16	13.34	0.696	0.698	6.48	860
MoS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoS ₂ /FTO	2.77	15.68	0.72	0.634	7.16	861
MoS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoS ₂ /FTO	25.77	15.92	0.73	0.615	7.14	862
MoS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoS ₂ /FTO	2.86	19.6	0.795	0.36	6.6	863
MoSe ₂ /WS ₂	FTO/TiO ₂ /N719/I [–] /I ₃ [–] /MoSe ₂ /WS ₂ /FTO	18.3	23.1	0.69	0.651	9.92	842

with MoS₂/RGO CEs have shown PV characteristics ($\eta = 6.0\%$, $J_{SC} = 12.51 \text{ mA cm}^{-2}$, $V_{OC} = 0.73 \text{ V}$, and $FF = 0.66$) comparable to those of Pt-based DSSCs ($J_{SC} = 13.42 \text{ mA cm}^{-2}$, $V_{OC} = 0.72 \text{ V}$, $FF = 0.66$, and $\eta = 6.38\%$).⁸⁶³ Li *et al.* prepared RGO-NiS₂ NP hybrids to develop CEs with excellent electrocatalytic activity toward I₃[–] reduction.⁸⁶⁵ The fabricated DSSCs using the NiS₂/RGO-based CE exhibited an η value of $\sim 8.55\%$, which was higher than that of the DSSC using either NiS₂-based ($\sim 7\%$) or RGO-based (~ 3.14) CE, as well as Pt-based CE ($\sim 8.15\%$).⁸⁶⁴

The DSSCs using CE based on NiO NPs/RGO hybrids have shown an η value of $\sim 7.42\%$, which was comparable to that of a conventional Pt-based DSSC ($\sim 8.18\%$).⁸⁶⁶

The NiO NPs/RGO hybrids exhibited lower R_{CT} value ($1.93 \Omega \text{ cm}^2$) compared to those based on NiO-based ($44.39 \Omega \text{ cm}^2$) and GO-based ($12.19 \Omega \text{ cm}^2$) CEs.⁸⁶⁵ Experimental investigations indicated that the synergic effects of two different low-dimensional carbon materials, such as CNT/graphene nanoribbons (CNT/graph-nRib), can be used to further amplify the CE catalytic activity of the single nanomaterial.⁸⁰⁶

More recently, Zhai *et al.* obtained an η value of $\sim 8.3\%$ in porphyrin-sensitized DSSCs using N-doped GNP-based CE [Co-(bpy)₃]^{3+/2+} redox complexes.⁸²² The obtained result was the consequence of better electrocatalytic activity in comparison to that of the Pt-based CE, whose corresponding cell reached an η value of 7.95% .⁸²² The performance increase was ascribed to a higher number of catalytic sites, due to the introduction of pyridinic and pyrrolic N into the carbon-conjugated lattice, compared to the GNPs.⁸²²

Shen *et al.* synthesized NiS/RGO-based CE with a material mass ratio varying from 0.2 up to 0.6 through a low-temperature hydrothermal method.⁸⁶⁷ The NiS/RGO hybrid-based CE exhibited the best catalytic property for the NiS:RGO mass ratio of 0.4%, yielding a DSSC with an η value of 8.26% , a value much higher than that of pristine RGO-based or NiS-based references (1.56% and 7.41% , respectively).⁸⁶⁶ The obtained results demonstrated that a correct load of NiS hinders the agglomeration of RGO flakes, favoring the diffusion of electrolyte into the NiS/RGO network.⁸⁶⁶

Zhou *et al.* synthesized graphene-wrapped CuInS₂ hybrids to be used as the CE material.⁸⁶⁸ The DSSCs based on CuInS₂/RGO as CE achieved an η value of 6.4% , which was comparable to that of Pt-based CE (6.9%).⁸⁶⁷ Huo *et al.* developed a sponge-like CoS/RGO-based CE with a low R_{CT} value of $3.59 \Omega \text{ cm}^2$.⁸⁶⁹ The corresponding DSSCs have shown an η value of 9.39% .⁸⁶⁸

Li *et al.* synthesized a nanostructured architecture of 3D bismuth sulfide (Bi₂S₃) microspheres on RGO through a solvo-thermal route.⁸⁷⁷ The as-produced architecture was used as the CE for DSSCs.⁸⁷⁶ By combining the characteristics of direct-bandgap Bi₂S₃ semiconductor (low bandgap of 1.7 eV and absorption coefficient of the order of $10^4\text{--}10^5 \text{ cm}^{-1}$) with outstanding carrier transfer properties of RGO, an η value ~ 3 times greater than that of DSSCs with 3D Bi₂S₃ without RGO (1.9%) was achieved.

Chen *et al.* prepared GQDs through a chemical oxidation approach to dope conductive polymers (polypyrrole (PPy)) on FTO glass as the CE for DSSCs.⁸²¹ The as-prepared DSSCs displayed an η value (*i.e.*, 5.27%) lower than that of Pt-based



Table 9 Summary of the PV performance of DSSCs using 2D material-based hybrid CEs

Material	Device structure	PV parameters					
		R_{CT} (Ω cm ²)	J_{SC} (mA cm ⁻²)	V_{OC} (V)	FF (—)	η (%)	Ref.
MoS ₂ /graphene	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /MoS ₂ /graphene	24.42	12.41	0.71	0.68	5.98	844
GNS	FTO/TiO ₂ /dye/I ⁻ /I ₃ ⁻ /GNS	6.24	11.99	0.754	0.30	2.68	843
MoS ₂ /GNS	FTO/TiO ₂ /dye/I ⁻ /I ₃ ⁻ /MoS ₂ /GNS	2.34	12.79	0.773	0.59	5.81	
RGO/NiS ₂	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /NiS ₂ /RGO	2.90	16.55	0.749	0.69	8.55	864
Bi ₂ S ₃ /RGO	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /Bi ₂ S ₃ /RGO	9.2	12.20	0.75	0.60	5.5	876
RGO/NiO	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /NiO/RGO	1.93	15.57	0.763	0.624	7.42	865
CuInS ₂ /graphene	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /CuInS ₂ /graphene	2.30	14.20	0.743	60.7	6.40	867
CoS/RGO	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /CoS/RGO	3.59	19.42	0.764	0.633	9.39	868
NiS/RGO	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /NiS/RGO	7.06	17.05	0.778	0.623	8.26	866
MoS ₂ /graphite	FTO/TiO ₂ /dye/I ⁻ /I ₃ ⁻ /MoS ₂ /graphite	8.05	15.64	0.685	0.67	7.18	870
TiS ₂ /graphene	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /TiS ₂ /graphene	0.63	17.76	0.72	0.685	8.80	858
WO _x /carbon	FTO/TiO ₂ /N719dye/I ⁻ /I ₃ ⁻ /WO _x /carbon/FTO	12.70	14.30	0.705	0.591	6.00	871
WO _x @WS ₂ /carbon	FTO/TiO ₂ /N719dye/I ⁻ /I ₃ ⁻ /WO _x @WS ₂ /carbon/FTO	0.88	15.48	0.720	0.695	7.71	870
MoS ₂ /graphene	FTO/TiO ₂ /N719dye/I ⁻ /I ₃ ⁻ /MoS ₂ /graphene/FTO	34.02	20.5	0.800	0.42	8.1	862
MoS ₂ /SnS ₂	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /MoS ₂ /SnS ₂ /FTO	0.32	15.99	0.73	0.65	7.6	872
NiSe/GNS _{0.50}	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /NiSe ₂ -graphene (1:0.50)	1.92	16.73	0.75	0.68	8.62	877
WSe ₂ /MoS ₂	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /WSe ₂ /MoS ₂ /FTO	44.42	16.89	0.69	0.724	8.44	873
Polyaniline/graphene	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /polyaniline/graphene	20.1	15.5	0.787	0.62	7.45	874
NiO/NiS/graphene	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /NiO/NiS/graphene	23.2	4.86	0.76	0.56	2.10	875
Co-Mo-S anchored on nitrogen-doped graphene (NG)	FTO/TiO ₂ /N719/I ⁻ /I ₃ ⁻ /Co-Mo-S anchored on nitrogen-doped graphene (NG)	—	7.22	0.49	0.44	1.18	876

reference devices ($\eta \approx 6.02\%$), but $\sim 20\%$ higher compared to that of DSSCs based on PPY as the CE (4.46%).⁸²¹

Murugadoss *et al.* grew NiSe NPs on GNSs with different mass ratios to obtain NiSe/GNS_x ($x = 0.25$ to 1.00) nanohybrids by an *in situ* hydrothermal process.⁸⁷⁸ This method takes advantages of the high SSA of GNSs to homogeneously immobilize NiSe NPs on top of them acting as the catalytic sites.⁸⁷⁷ The nanohybrid with a mass ratio of 1:0.50 (NiSe/GNS_{0.50}) exhibited the highest electrocatalytic activity and electrolyte diffusion among the different hybrid compositions.⁸⁷⁷ Thus, the DSSC with NiSe/GNS_{0.50} CE exhibited an η value of 8.62%, which is higher compared to a standard Pt-based DSSC ($\eta = 7.68\%$).⁸⁷⁷ The NiSe/GNS_{0.50} CE exhibited a superior PV performance compared to both Pt and pristine NiSe CEs.⁸⁷⁷ Compared to the hybrid NiSe/GNS_{0.50} CE, the lower performance of the NiSe electrode, when integrated in a DSSC ($\eta = 7.18\%$), was attributed to the aggregation of NiSe NPs and the poor connections between the NPs, which decrease the number of electrocatalytic active sites as well as the electrical conductivity of the CE.⁸⁷⁷ The optimal performance of NiSe/GNS_{0.50} CE is determined by the interfacial electron transfer pathways of GNSs and the exceptional catalytic activity of NiSe toward I₃⁻ reduction at the CE/electrolyte interface.⁸⁷⁷

Table 9 summarizes the PV performance of DSSCs using 2D material-based hybrid CEs.

5.2.4 Bifacial DSSCs using 2D material-based transparent CEs. Research on transparent and cost-effective CEs is a persistent objective in the development of bifacial DSSCs. Transparent or semitransparent electrodes can be used for building-integrated photovoltaics (BIPVs) to make use of light from the interior of the building as well as the outside.^{879–881} So far, efficient solution-processed transparent CEs have been reported using both PEDOT and binary-alloy transition metal chalcogenides (M–Se; M = Ni, Co, Fe, Cu, and Ru). For example, bifacial DSSCs with CEs composed

by a metal selenide achieved front η values of 8.3%, 7.8%, 6.4%, 7.6%, and 9.2% for Co_{0.85}Se, Ni_{0.85}Se, Cu_{0.50}Se, FeSe, and Ru_{0.33}Se, respectively, which were even higher than that of a cell with an electrode based on standard Pt (6.1%).⁸⁸² The corresponding rear η values were 4.6%, 4.3%, 4.2%, 5.0%, 5.9%, and 3.5% for devices based on Co_{0.85}Se, Ni_{0.85}Se, Cu_{0.50}Se, FeSe, Ru_{0.33}Se, and Pt, respectively. Besides, PEDOT can provide an optimal conductivity–transparency trade-off, while being suitable for large-scale and cost-effective production.⁸⁸³ However, the catalytic performance of PEDOT CE alone is inferior compared to those of Pt CE or other metal-based CEs. Therefore, PEDOT has been combined with other catalytic materials to improve the performance of bifacial DSSCs. In this context, Chen *et al.* developed transparent CEs of PEDOT/N-doped graphene (NG) for bifacial DSSCs, achieving an η value of 8.3%, which is higher than that of DSSCs using Pt CE (8.17%).⁸⁸⁴ In a recent study, Xia *et al.* prepared layered CoSe₂ nanorods with lengths of 70–500 nm and widths of 20–60 nm by a one-step hydrothermal reaction and used them as the CE material.⁸⁸⁵ The resulting bifacial cells using a PVDF quasi-solid-state electrolyte revealed that the η values for the front and rear irradiation of CoSe₂ CE-based devices reached 8.0% and 4.2%, which are higher than those achieved with Pt CE (7.4% and 4.0%, respectively). More recently, Xu *et al.* reported the preparation of transparent organic–inorganic hybrid composite films of MoS₂/PEDOT to take full advantage of the conductivity and electrocatalytic properties of the two components.⁸⁸⁶ Researchers synthesized MoS₂ by the hydrothermal method. MoS₂ dispersions were spin coated to form an MoS₂ layer and subsequently prepared PEDOT films deposited on top of the MoS₂ film by the electrochemical polymerization to form composite CEs.⁸⁸⁵ DSSCs using the MoS₂/PEDOT composite CE exhibited an η value of 7% under front illumination and 4.82% under rear illumination.⁸⁸⁵ Compared with other DSSCs based on PEDOT CE or Pt CE, DSSCs using MoS₂/PEDOT composite CE improved the front η by 10.6% and



6.4%, respectively.⁸⁸⁵ As discussed above, the DSSCs assembled with transparent CEs based on TMDs and graphene-like materials exhibit η comparable or even higher than those of semitransparent Pt-based DSSCs. Such performances achieved with Pt-free CEs are promising to reduce the power-to-weight ratio and total cost of bifacial DSSCs, paving the way toward 2D material-based DSSCs for smart windows, power generators, and panel screens.

5.3 Summary and outlook

The global DSSC market size was valued at USD 90.5 million in 2019 and is expected to grow at a compound annual growth rate (CAGR) of 12.4% from 2020 to 2027.⁸⁸⁷ The global DSSC market is segregated into portable charging, BIPV, embedded electronics, outdoor advertising, and automotive. In this scenario, BIPV represents a strategic sector, in which DSSCs reached an η value higher than 25% (up to a record-high value of 32% at 1000 lux).^{888–890} Regarding outdoor applications, the advent of PSCs has outclassed the use of DSSCs as single-junction devices, the η value of DSSC being significantly inferior to that of PSCs.⁸⁹⁷ However, DSSCs still represent an interesting PV technology to make cost-effective and efficient tandem systems, including those based on PSCs as sub-cells. Overall, the advancements achieved in DSSCs using 2D materials might be applied to the most promising configuration for convenient applications, as discussed above. In fact, the current record-high η value of DSSCs was reached using GNPs as the CE⁸²⁹ (previous record of 13% was also achieved using graphene-based CEs),⁸³⁰ unequivocally proving the potential of 2D materials for both improving the PV performance and decreasing the cost of traditional PV based on Pt CEs.^{891,892} Prospectively, lifecycle assessment can provide a useful methodological framework to calculate the eco-profiles of solution-processed 2D material-based DSSCs with a future-oriented perspective. Importantly, DSSCs are the third-generation hybrid-organic technology that reached the highest maturity in terms of manufacturing, reporting several pilot-line semi-industrial production lines.^{893,894} Overall, the synergistic use of 2D materials, novel dyes, and advanced anode structures are expected to play a major role in the further optimization of DSSC technology, both in the indoor and outdoor PV market.

6. PSCs

During the last few years, the rapid emergence of perovskite PV technology in the global energy scenario has strongly attracted efforts from the scientific community.^{895–897}

Perovskite semiconductors have been used in SCs since the pioneering work of Kojima *et al.* who proposed the perovskite as a sensitizer in a DSSC, achieving an η value of 3.8%.⁸⁹⁴ Thereafter, much progress has been achieved in the last 12 years, achieving certified η exceeding 25%,⁸⁹⁸ which makes PSCs among the most promising class of devices in the broad context of 3rd-generation PV technologies.⁸⁹⁷

The term perovskite refers to a broad class of crystals sharing the crystalline structure of calcium titanate (CaTiO_3).⁹⁰⁰

Generally, the crystallographic structure is indicated with the chemical formula ABX_3 , where A is a small organic or inorganic cation that occupies a cube-octahedral⁹⁰¹ site, B is a metal cation in the center, and X is a halogen anion in an octahedral site.⁸⁹⁹

The perovskite structure widely used in SCs is an organic-inorganic hybrid based on an organometallic halide material. In particular, A can be methylammonium CH_3NH_3^+ (MA), formamidinium (FA), or Cs; B is commonly the lead ion Pb^{2+} (even though ions of Sn, Ge, Sb, Bi are also used), and X is an halide, typically iodide or bromide (I^- or Br^-).⁹⁰² Thus, in the perovskite structure, A, located in a cage, is surrounded by four BX_6 octahedra, and can partially move inside the cage⁹⁰¹ (Fig. 17). Organic-inorganic halide perovskites offer attractive prospects in developing high-performance SCs,^{903–905} low processing costs and facile fabrication processes.^{906,907} In fact, due to their particular crystallographic structure and the peculiar choice of components,⁹⁰⁸ organic-inorganic halide perovskites exhibit outstanding and unique optoelectronic properties, including large and broad absorption spectrum,⁹⁰⁹ immediate charge generation within the bulk material (due to very low exciton binding energy),⁹¹⁰ optimal ambipolar charge transport with a long charge diffusion length (~ 100 nm for $\text{CH}_3\text{NH}_3\text{PbI}_3$ and ~ 1 μm for $\text{CH}_3\text{NH}_3\text{PbI}_{3-x}\text{Cl}_x$),⁹¹¹ efficient charge injection into the CTLs, and low trap density, which points them as “defect-tolerant” materials.^{906,912–914} In addition, chemical modifications of the constituents enable the tuning of the material properties, for example, the E_g , which spans over a range wider than 1 eV. The architecture of a PSC consists of a perovskite active layer sandwiched between an HTL and an ETL. More specifically, two PSC structures have been mainly developed, *i.e.*, mesoscopic^{894,906} and planar⁹⁰⁵ structures, and both of them can be found in n-i-p (direct) or p-i-n (inverted) configurations (Fig. 18).⁹¹⁵ The mesoscopic architecture is so called because a mesoporous oxide layer is used as the ETL in which the perovskite is infiltrated.

In detail, mesoscopic PSCs are composed of different layers.^{894,906,916} The first one is a TCE (*e.g.*, FTO or ITO),

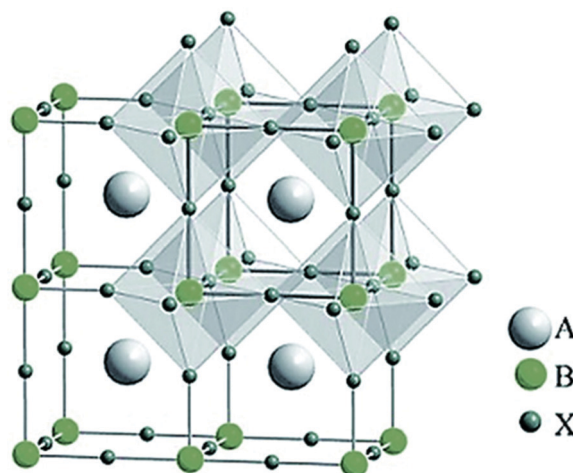


Fig. 17 The basic perovskite structure (ABX_3). Adapted from ref. 899.



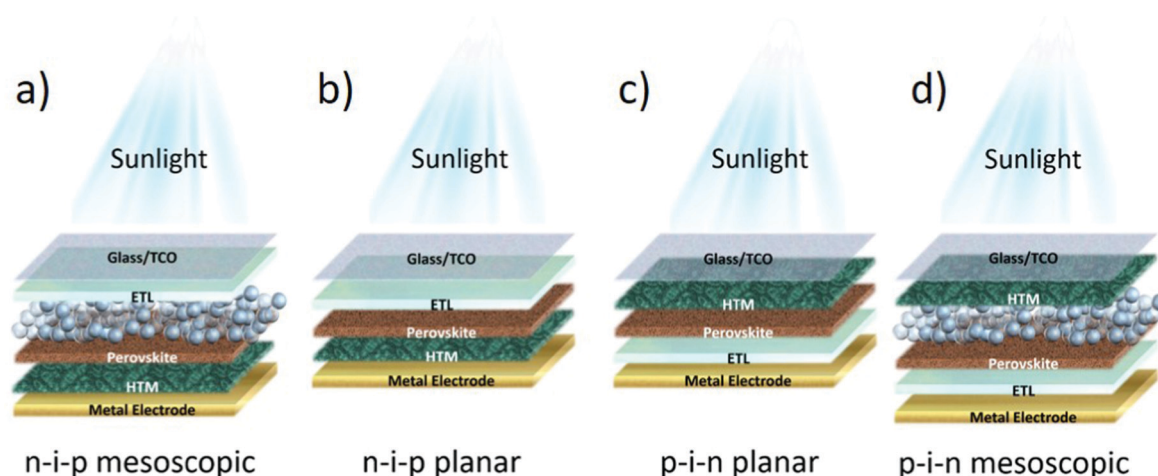


Fig. 18 (a) Mesoscopic n-i-p, (b) planar n-i-p, and (c) planar p-i-n and mesoscopic p-i-n PSC structures.

deposited on the bottom of the glass surface and acting as the front transparent electrode. Subsequently, a compact ETL is deposited onto the TCE. The compact ETL is typically made of TiO_x ⁹⁰⁶ or ZnO ^{917,918} (thickness ranging from 10 to 400 nm, depending on the material), which can be deposited using different techniques (e.g., spray pyrolysis,⁹¹⁹ sol-gel,⁹²⁰ DC magnetron sputtering,^{921,922} electrodeposition,^{923,924} electron-beam evaporation,⁹²⁵ and pulsed laser deposition^{926,927}). Then, a layer of mesoporous oxide is obtained by depositing a paste typically containing colloidal NPs (preferably TiO_2 ,^{894,906} ZrO_2 ,^{928,929} Al_2O_3 ,⁹³⁰ and SiO_2 ^{931,932}) using various techniques (e.g., sol-gel,^{933,934} doctor blade,⁹³⁵ spin coating,⁹³⁶ spray coating,⁹³⁷ electrospray deposition,⁹³⁸ slot-die coating,^{939,940} inkjet printing,⁹⁴¹ and pulsed laser deposition^{733,942,943}). For glassy substrates, the device is subsequently heated (e.g., at 450–550 °C for 30 min for the calcination of TiO_2) in order to evaporate the organic binder and to create an electromechanical connection between the NPs.^{902,944} For heat-sensitive plastic substrates, the mesoporous layer is alternatively formed by means of low-temperature processes, such as microwave sintering,⁹⁴⁵ laser sintering,^{946,947} intense pulsed light sintering,⁹⁴⁸ and NIR sintering.^{949,950} Thereafter, a perovskite layer (generally formed by one or more organic cations, such as methylammonium (MA) and formamidinium (FA), and one or more inorganic compounds, such as PbI_2Cl , Pb_3 , or PbI_2Br) is infiltrated in the mesoporous electrodes by various techniques,⁹⁵¹ e.g., spin coating,^{902,952–955} spray casting,^{956–959} physical vapor deposition,^{960,961} thermal evaporation,⁹⁶² dip coating,⁹⁶³ slot-die coating,⁹⁶⁴ roller coating,⁹⁶⁵ and bar coating.⁹⁶⁶ Subsequently, the resulting film is often crystallized through a heating step at 70–100 °C for 10–30 min, depending on the perovskite composition and deposition method.⁹⁵⁰ On the so-formed photoelectrode, an HTL (e.g., P3HT,^{967–969} spiro-OMeTAD,^{970,971} PTAA,⁹⁷² PEDOT,⁹⁷³ copper thiocyanate (CuSCN),^{974,975} and triphenylamine-based molecules^{976,977}) is deposited, typically *via* solution-based techniques, e.g., spin coating, spray casting, inkjet printing, and slot-die coating. Lastly, the mesoscopic PSC is completed by depositing a metal contact as the CE (e.g., Au, Ag, and Al). Alternatively, a planar

architecture can be used as a simpler PSC structure.⁹⁰⁵ The main difference between a planar direct configuration (n-i-p structure) and mesoscopic devices is the use of a single compact n-type metal oxide layer (e.g., TiO_2 ,⁹⁷⁸ ZnO ,^{979–981} and SnO_2 ^{982–986}) in the former rather than a combination of both compact and mesostructured scaffolds.^{987,988} Differently, in an inverted planar configuration (p-i-n structure),⁹⁰⁵ a p-type material (e.g., NiO_x ,^{989–991} PEDOT:PSS,^{992,993} CuSCN ,⁹⁹⁴ CuI ,⁹⁹⁵ Cu oxides,^{996,997} and V_2O_x ⁹⁹⁸) is used as the bottom HTL, while PCBM is the typically used ETL.^{999–1001} As a matter of fact, several potential material/structure combinations can be designed to implement new PSC structures. In fact, on one hand, the correct choice of materials is crucial for determining both optical and electronic properties (e.g., bandgap and commensurate absorption spectra, μ , charge diffusion lengths, *etc.*). On the other hand, material arrangement in the different architectures plays a crucial role in the overall PSC performance.

Despite the undoubted interest in perovskites, mainly owing to their low cost and efficiency compared to the technologies currently in the market, PSCs currently suffer from low stability, a big challenge for their market uptake.¹⁰⁰² Perovskite instability has been correlated to both intrinsic^{1003–1006} and extrinsic factors,¹⁰⁰⁵ mainly associated with moisture^{1007,1008} and oxygen exposure,^{1006,1007} as well as UV radiation,^{1009,1010} high-temperature exposure,¹⁰¹¹ and electrical biases.^{1012,1013} In detail, under prolonged working conditions, PSCs often exhibit structural degradation of perovskites (as well as other component layers). For example, ion migration from the perovskite to metal and *vice versa*, as well as perovskite decomposition through the volatilization of perovskite species can cause the rapid failure of PSCs.^{1005,1014}

Although some extrinsic degradation factors, such as oxygen, moisture, and UV exposure can be avoided by means of new strategies to encapsulate the assembled device,^{1015–1017} the intrinsic structural instability can be addressed by designing more stable perovskites^{1018–1021} or by adding crosslinking additives,^{1022–1025} ionic liquids additives,^{1026–1028} dopants,^{1029–1031} and interlayers^{1032–1035} that can stabilize the crystal structure.



Recently, pressure-tight polymer (polyisobutylene)/glass stack encapsulation has been shown to inhibit intake moisture, while preventing the outgassing of decomposition products of the perovskite.¹⁰¹⁶ Consequently, the decomposition reaction for a prototypical Cs-containing triple-cation perovskite, namely, $\text{Cs}_{0.05}\text{FA}_{0.8}\text{MA}_{0.15}\text{Pb}(\text{I}_{0.85}\text{Br}_{0.15})_3$, were suppressed, permitting the devices to pass the International Electrotechnical Commission (IEC) 61215:2016 Damp Heat and Humidity Freeze tests.¹⁰¹⁶

In this context, (1) the exploitation of solution-processed GRMs to engineer the device interface^{1036–1040} and (2) the introduction of 2D perovskites as active materials^{111,1016,1041–1043} have recently been revealed as two main routes for the realization of highly efficient and durable PSCs. In the first case, the possibility to chemically or thermally modify GRMs allows their oxygen vacancy/defect/functional group concentration to be controlled to attain the desired optoelectronic properties.¹⁰⁴⁴ Recent advances in the production and processing of GRMs allowed their effective use in the PSC structures,^{596,1037} for example, as ETLs^{1045–1047} or HTLs^{1048,1049} as well as interlayers at the perovskite/CTL interface.^{1050,1051} In particular, GRM-induced improvement in charge transport and collection at the electrodes allows the η value to be significantly enhanced.^{1052,1053} Moreover, the use of GRMs in PSCs results in a remarkable increase in the device's stability under several stress conditions, by preventing interfacial perovskite degradation.^{1039,1054–1059} In the second case, 2D perovskites have demonstrated superior moisture stability compared to the 3D counterparts, offering new approaches to stabilize PSCs.^{111,1060} Owing to their versatile structure, 2D perovskites enable the *ad hoc* tuning of their optoelectronic properties through compositional engineering.^{111,1061} Finally, recent achievements have demonstrated the possibility to combine 3D and 2D perovskites to simultaneously boost the device efficiency and stability, opening the route toward advanced mixed-dimensional PSCs.^{111,1062}

In the subsequent sections, the use of GRMs and 2D perovskite layers into CTLs and perovskite, as well as their utilization as buffer layers and front/back electrodes, will be discussed.

6.1 ETLs

As shown in Fig. 18, the configurations of a PSC require a perovskite light-absorbing layer interposed between a wide-bandgap ETL and HTL, which assist charge carrier transport to the negative and positive electrodes, respectively.^{1063,1064} Meanwhile, the CTLs must prevent charge transport toward the undesired electrode.^{1062,1063}

In mesoscopic PSCs, the generated electrons have to travel through the mesoporous ETL, which plays a crucial role in terms of efficiency and stability of the whole device.^{1065,1066} A large variety of materials have been used as ETLs to efficiently extract photoexcited electrons in the perovskite layer.¹⁰⁶⁷ It is worth pointing out that the mesoporous ETL can be conductive (*e.g.*, TiO_2 , ZnO , and NiO) or insulating (*e.g.*, Al_2O_3 , ZrO_2 , and SiO_2). In the first case, the mesoporous layer acts as an ETL, while in the second one, it provides a scaffold functionality.

Due to the capacity to prevent leakage currents, and hence to prevent cell shunting, TiO_2 is the most established ETL for PSCs.^{696,1068} Mesoscopic PSCs using anatase mesoporous TiO_2

(mTiO_2) with NPs in the 10–30 nm size range have shown η often exceeding 21%.^{902,1069} Nanomaterials based on ZnO could also be promising semiconducting metal oxides alternative to TiO_2 , owing to their wide bandgap (~ 3.37 eV), large exciton binding energy (~ 60 meV), high μ_e , unique photoelectric properties, optical transparency, electric conductivity, and piezoelectric properties.^{1070–1072} To overcome the disruptive effect of moisture on the perovskite structure and to prolong the lifetime of the devices, ZnO QDs have also been exploited as an alternative scaffold to other ZnO nanostructures, owing to their tunable bandgap and chemical inertness.¹⁰⁷³ Lastly, ZnO offers the benefit to be easily processed at low temperatures, opening the possibility to develop efficient low-temperature fabricated mesoscopic PSCs.¹⁰⁷⁴

In order to increase the V_{OC} of PSCs, mesoporous Al_2O_3 , ZrO_2 , and SiO_2 have been investigated as a scaffold to alternative mTiO_2 .^{1075–1078} For example, a mesoporous Al_2O_3 (mAl_2O_3) layer was used to transport photoexcited electrons throughout the perovskite layer, allowing $\eta > 12\%$ to be reached.¹⁰⁷⁹

Ternary oxides, such as SrTiO_3 ,^{1080,1081} Zn_2SnO_4 ,¹⁰⁸² and BaSnO_3 ¹⁰⁸³ have also been used to obtain better performing devices in terms of η . For example, SrTiO_3 exhibits the same perovskite structure with μ_e and CB higher than those of TiO_2 .^{1084,1085} Thus, SrTiO_3 -based PSCs showing V_{OC} higher than 1 V have been reported.¹⁰⁸⁰

In order to boost the electrical performance of PSCs, it is necessary to precisely control the charge carriers' pathway along the entire device,^{1086,1087} by avoiding losses due to photon thermalization or carrier-trapping processes and improving faster electron injection. In fact, charge carrier injection at the perovskite/ETL interface is strongly limited by interfacial charge recombination when the interfaces are not properly engineered, such as in presence of nonoptimized energy-level alignment.¹⁰⁸⁸ Likewise, poor charge transport in the CTLs^{1089,1090} severely limits charge collection toward the electrodes, reducing I_{SC} and FF ^{1091–1093} and therefore the η value.

Several strategies have been reported in the literature to enhance the charge transport and extraction properties at the interface between the perovskite/ETL. These strategies include TiO_2 doping^{1094,1095} and the use of different TiO_2 nanostructures,^{1096–1098} as well as the modification of interfacial energy-level alignment through the incorporation of appropriate buffer layers.^{1036,1099}

In this framework, numerous solutions have been proposed to facilitate electron extraction and to increase the conductivity by taking advantage of GRMs.^{1036,1100–1102}

The use of graphene with nanostructured ZnO or TiO_2 in PSCs results in a higher photocurrent density and consequently better device performance compared to the reference device without graphene.¹⁰⁹⁹ Wang *et al.* developed low-temperature-processed nanocomposites of pristine graphene nanoflakes and anatase- TiO_2 NPs to be used as the ETL in mesoscopic PSCs (Fig. 19a).¹¹⁰⁰ The observed decrease in the series resistance, as well as a decrease in charge recombination, determined an improvement in the device performance, achieving an η value of 15.6% (Fig. 19b).¹¹⁰⁰ The use of graphene nanoflakes, with an appropriate ϕ_{W} (*i.e.*, 4.4 eV), reduced the energy barrier between



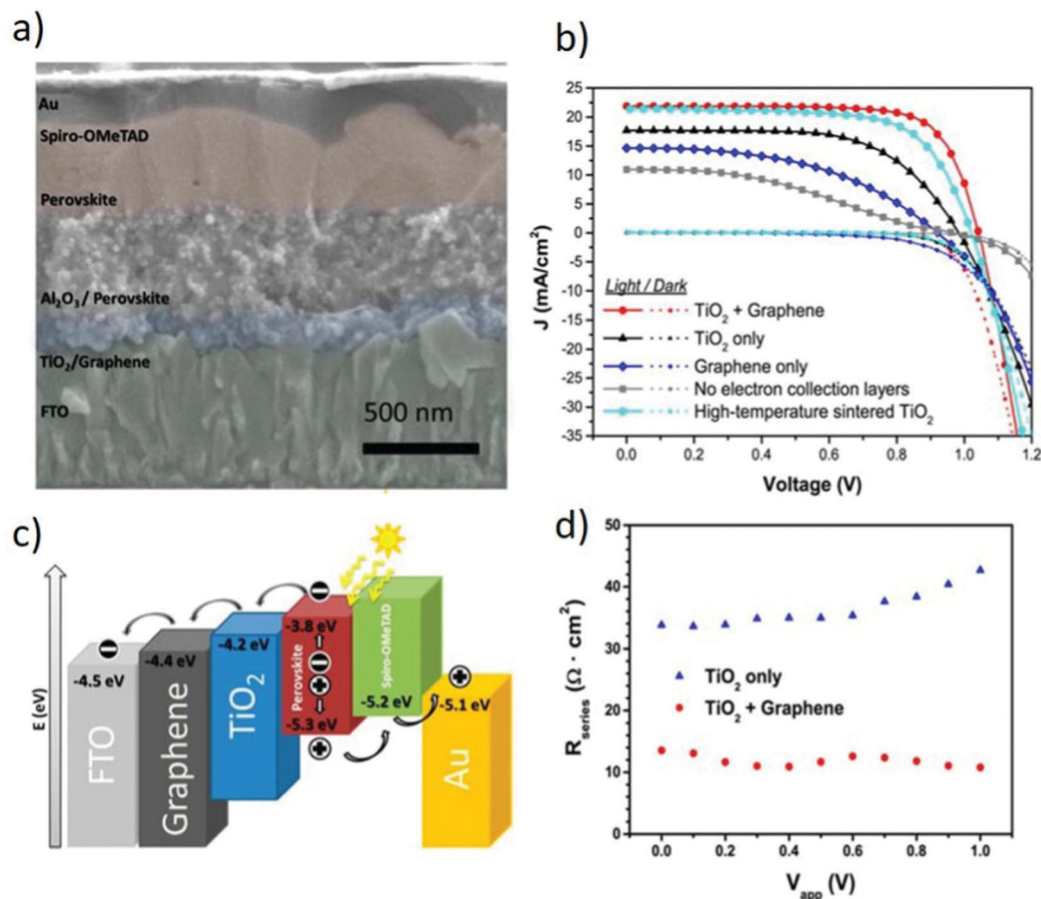


Fig. 19 (a) Cross-sectional SEM image of a PSC based on a graphene–TiO₂ composite as the ETL. (b) *J*–*V* curves measured for PSCs with different ETLs under solar irradiation and in the dark (c). Energy levels of a PSC based on a graphene–TiO₂ composite as the ETL. (d) Series resistances of PSCs using pristine TiO₂ and graphene–TiO₂ composite as the ETLs. Reprinted with permission from ref. 1100, Copyright 2013, American Chemical Society.

the LUMO of TiO₂ (4.2 eV) and Φ_w of FTO (4.5 eV), leading to better electron collection through the ETL (Fig. 19c).¹¹⁰⁰ In addition, the μ value of graphene flakes increased the electrical conductivity of the graphene–TiO₂ ETL compared to bare TiO₂ (Fig. 19d).¹¹⁰⁰ GRMs have also been used as the interlayer between perovskite and mTiO₂. Zhu *et al.* reported that the insertion of an ultrathin layer of GQDs between the perovskite and mTiO₂ impacts the PSC performance, increasing the η value from 8.81% up to 10.15%.¹¹⁰¹ The insertion of a GQD interlayer causes strong quenching of perovskite photoluminescence at ~ 760 nm due to a reduced electron extraction time (90–106 ps) in the presence of GQDs.¹¹⁰¹ This means that the GQDs permit an efficient electron transfer from the photo-absorber to the acceptor, resulting in efficient electron extraction.¹¹⁰¹

More recently, Tavakoli and co-workers developed a new and simple chemical process to synthesize a quasi-core-shell structure of ZnO NPs/RGO to be used as the ETL in PSCs.¹⁰⁹⁹ In fact, RGO passivates the ZnO NP surface, preventing degradation reactions at the perovskite/ETL interface caused by the presence of the hydroxide group.¹⁰⁹⁹ Furthermore, the ZnO/RGO ETL improves the electron transfer at the perovskite/ETL interface, increasing the EQE and photocurrent density.¹⁰⁹⁹ Thus, the use of RGO increased η up to 15.2% on rigid PSCs using FTO-coated substrates, while

flexible devices on ITO-coated PET achieved an η value of 11.2%.¹⁰⁹⁹ In a subsequent work, Tavakoli *et al.* reported a very high performing PSC ($\eta = 17.2\%$) using a reduced-graphene scaffold (rGS) obtained through EpD.¹¹⁰³ The authors fabricated a porous 3D scaffold of graphene with a large SSA that enabled a higher loading of perovskite materials.¹¹⁰² The addition of rGS improved the carrier transport of the PSC, yielding an η value enhancement of $\sim 27\%$ compared to the conventional device.¹¹⁰² Besides, sealed rGS-based devices retained 80% of their initial η for a time as long as a month under ambient conditions ($\sim 65\%$ humidity).¹¹⁰² Ameen and co-workers used a graphene thin film as the barrier layer between O₂ plasma-treated ITO-PET and the ETL based on ZnO QDs.¹¹⁰⁴ A subsequent atmospheric plasma jet (APjet) treatment of ZnO QD ETL improved the interfacial contacts, modifying the surface properties of the ITO-PET/Gr/ZnO QD structure.¹¹⁰³ The use of a graphene interlayer and APjet treatment of ZnO QDs improved the carrier transport and collection efficiency.¹¹⁰³ Moreover, modification with regard to the surface area, pore size, and porosity caused by the APjet treatment allowed perovskite infiltration to be optimized.¹¹⁰³ Thus, the fabricated ITO-PET/Gr/ZnO QDs/CH₃NH₃PbI₃/spiro-OMeTAD/Ag flexible PSCs reached a high η value of $\sim 9.73\%$, along with a J_{SC} value of ~ 16.8 mA cm⁻², V_{OC} of ~ 0.935 V, and FF of ~ 0.62 .¹¹⁰³



These performances outperformed those of the PSCs fabricated with ITO-PET/graphene and ZnO-QDs/graphene/ITO-PET structures.¹¹⁰³ Graphene-based interface engineering through the incorporation of an additional buffer layer represents an effective strategy to improve the PV performance while overcoming oxygen- and moisture-induced instability. For example, Agresti *et al.* proposed a new, efficient PSC structure by including a GO-Li interlayer between TiO_2 and the perovskite.¹⁰⁵¹ The main effect of the GO-Li interlayer is the enhancement—compared to the reference devices—of both J_{SC} (+10.5%) and FF (+7.5%), positively affecting both η and long-term stability.¹⁰⁵¹ In particular, this work pointed out to improved charge extraction/injection at the negative photoelectrode when GO-Li was used as the ETL.¹⁰⁵¹ In fact, the GO-Li interlayer favors the passivation of oxygen defects/vacancies in mTiO_2 , eliminating reactive centers susceptible to moisture attack. Such an effect improved the stability of devices, which have shown an enlarged lifetime without encapsulation during aging tests. A similar interface strategy was used to further increase the η and stability of PSCs using mTiO_2 doped with graphene flakes ($\text{mTiO}_2 + \text{G}$) and GO as an interlayer between the perovskite and HTL.^{1036,1105} These PSCs achieved a remarkable η value of 18.2% as a consequence of the improved charge-carrier injection/collection.¹⁰³⁶ In addition, the optimized PSCs improved their stability under several aging tests compared to the reference devices. In fact, when $\text{mTiO}_2 + \text{G}$ was used, the PSCs retained more than 88% of their initial η under prolonged 1 sun illumination at MPPT for a time as long as 16 h (Fig. 20a). Recently, time-of-flight secondary ion mass spectrometry (ToF-SIMS) 3D imaging and XPS depth profile analysis were used to evaluate the light-induced degradation of layers and interfaces both in mesoscopic PSCs with $\text{mTiO}_2 + \text{G}$ and graphene-free PSCs (Fig. 20b).¹¹⁰⁶ These results

demonstrated that the incorporation of graphene within mTiO_2 improves the stability of PSCs by limiting the light-induced back-conversion of $\text{CH}_3\text{NH}_3\text{PbI}_3$ into PbI_x and PbO_x species.¹¹⁰⁵ Therefore, the formation of iodine species was also reduced, impeding them to diffuse across the interface until modifying the Au electrode and mTiO_2 through the A-I and Ti-I bond formation.¹¹⁰⁵ Even more recently, femtosecond transient absorption measurements proved that the incorporation of graphene can stabilize the PSCs owing to the potential exploitation of the contribution of hot carriers to the η value of PSC (Fig. 20c).¹¹⁰⁷ In particular, these results demonstrated that the insertion of graphene flakes into mTiO_2 leads to stable values of carrier temperature.¹¹⁰⁶ In graphene-free PSCs aged over 1 week, the carrier temperature decreased from 1800 to 1300 K, while the graphene-based cell reported a reduction inferior to 200 K after the same aging time.¹¹⁰⁶ The stability of carrier temperature was associated to the stability of the perovskite embedded in $\text{mTiO}_2 + \text{G}$. Overall, all these results involving $\text{mTiO}_2 + \text{G}$ have opened the way for scalable large-area PSC production due to the use of GRMs in the form of dispersions and inks.²⁰⁵ In fact, by means of graphene and GRMs, Agresti *et al.* realized large-area (50.6 cm^2) perovskite-based solar modules (PSMs) with a remarkable η value of 12.6%.¹¹⁰⁸

Recently, a similar approach was followed by Cho *et al.*, which systematically investigated the role of RGO in PSCs by dispersing RGO into the mTiO_2 matrix to obtain highly efficient PSC ($\eta = 19.54\%$).¹¹⁰⁹ Moreover, the role of RGO has been demonstrated to be crucial to improve the transport and injection of photoexcited electrons.¹¹⁰⁸ Previously, several authors also used RGO as the dopant into a TiO_2 layer. Umeyama and co-workers doped both compact TiO_2 (cTiO_2) and mTiO_2 with RGO to increase the η value from 6.6% to 9.3%.¹⁰⁴⁶ To maximize

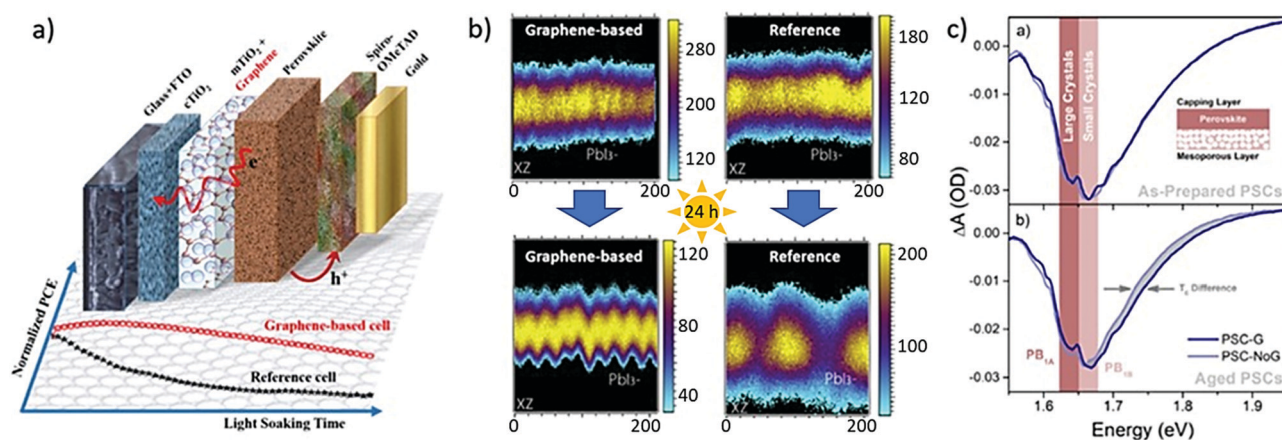


Fig. 20 (a) Graphene-based PSC energy-level alignment representation and η stability trends under prolonged light-soaking condition (1 sun) for both standard and graphene-engineered devices.¹⁰³⁶ (b) ToF-SIMS 3D analysis showing the reconstructed XZ distribution of PbI_3^- (from the $\text{CH}_3\text{NH}_3\text{PbI}_3$ absorber) in the as-deposited (upper part) and 24 h light-aged (lower part) PSCs. The PbI_3 signal decay suggests the progressive decomposition of the perovskite absorber material, which was always more severe in the reference PSC structure. Adapted from ref. 1105, Copyright 2018, Elsevier. (c) Transient absorption spectra acquired at a pump–probe time delay of 0.75 ps for (a) as-prepared and (b) aged PSC with $\text{mTiO}_2 + \text{G}$ (PSC-G) and graphene-free PSC (PSC-NoG). The photobleaching signal exhibits two peaks at 1.64 eV and 1.66 eV attributed to the absorption bleaching in large crystals of the capping layer and in small crystals of the mesoporous layer, respectively. Hot electron lifetime from the transient absorption measurements related to the degradation of small perovskite crystals wrapped in the mesoporous TiO_2 layer. When graphene is embedded into the mTiO_2 layer, the hot-carrier temperature is preserved over aging time by improving the device stability. Adapted from ref. 1106, Copyright 2019, American Chemical Society.

the charge transport properties in TiO_2 layers, the authors mixed TiO_2 with small quantities of GO, which was reduced to RGO during the subsequent calcination process.¹⁰⁴⁶

Han *et al.* reported RGO/ mTiO_2 nanocomposite ETL to reduce film resistivity and to increase the electron diffusion of pristine mTiO_2 .¹⁰⁴⁴ Consequently, they achieved an η value that was $\sim 18\%$ higher compared to the RGO-free reference PSC.¹⁰⁴⁴ Recently, GQDs have been similarly proposed for doping TiO_2 .¹¹¹⁰ To improve the I_{SC} value of SrTiO_3 -based PSCs, Wang *et al.* successfully incorporated graphene in mesoporous SrTiO_3 , reaching an η value of 10%, which is 46.0% higher than that achieved by the reference device.¹⁰⁸⁰ Mali *et al.* proposed RGO-grafted porous zinc stannate (ZSO) scaffold-based PSCs, which achieved a V_{OC} value of 1.046 V, J_{SC} of 22.5 mA cm^{-2} , η of 17.89%, and FF of 76%.¹¹¹¹ The performance of the proposed PSCs was ascribed to the presence of RGO in the ZSO scaffold, where it served as a highway track for the photogenerated electrons, facilitating electron injection from the perovskite into the ZSO CB.¹¹¹⁰

Recently, GRMs have been used to dope SnO_2 in planar PSCs. Zhu *et al.* proposed the incorporation of graphene into SnO_2 to improve the electron extraction efficiency, as well as to attenuate charge recombination at the ETL/perovskite interface.¹¹¹² Consequently, PSCs based on graphene-doped SnO_2 ETL exhibited η over 18% with negligible hysteresis.¹¹¹¹ In addition, the use of graphene as the ETL dopant enhanced the stability of the device, which retained 90% of the initial η after 300 h storage under the ambient condition with a relative humidity of $40 \pm 5\%$.¹¹¹¹

Following a similar strategy, Zhao *et al.* incorporated naphthalene diimide-graphene into SnO_2 ETLs to increase the surface hydrophobicity and to generate van der Waals interaction between the surfactant and perovskite.¹¹¹³ These effects led to η exceeding 20%.¹¹¹² As the peculiar interface engineering of planar PSCs based on SnO_2 ETL, 2D $\text{g-C}_3\text{N}_4$ has been recently proposed as a heat-resisting n-type semiconductor to modify the interfaces of ETL/perovskite and perovskite/HTL, respectively.¹¹¹⁴ The $\text{g-C}_3\text{N}_4$ structure can passivate the surface trap states of the MAPbI_3 light absorber through the formation of Lewis adducts between N and the undercoordinated Pb, by reducing the grain boundaries between the perovskite crystal particles. The as-realized cells reached an η value exceeding 19.6% with remarkable FF of over 80%.¹¹¹³ Moreover, new emerging 2D materials, including TiS_2 and SnS_2 , were recently used as the ETL in the n-i-p planar architecture.^{1044,1115,1116} For example, Huang and co-workers reported FTO/ TiS_2 /perovskite/spiro-OMeTAD/Au devices showing an η value of 18.8% when the TiS_2 -coated ITO film underwent UVO treatment.¹¹¹⁴ In fact, UVO can shift the TiS_2 -coated ITO WF to 4.64 eV, thus speeding up electron collection.¹¹¹⁴ Moreover, UVO-treated TiS_2 ETL-based devices also exhibited excellent device stability, retaining 95.8% of their initial η after 816 h of ambient storage (without any encapsulation).¹¹¹⁴ In addition, they maintained over 80% of their initial η after exposure to a high humidity environment (45–60 RH) for 100 h.¹¹¹⁴ Lastly, highly efficient ($\eta = 21.73\%$) n-i-p planar PSCs were fabricated by Huang *et al.* in 2019, employing a double layer of SnO_2 and 2D TiS_2 as the ETL.¹¹¹⁵ Highly efficient ($\eta > 20\%$)

n-i-p planar PSCs were also recently demonstrated using SnS_2 .¹⁰⁴⁴ Intermolecular Pb-S interactions between perovskite and SnS_2 were proposed to passivate the interfacial trap states.¹⁰⁴⁴ This effect can suppress charge recombinations and facilitate electron extraction, resulting in balanced charge transport at the ETL/perovskite and HTL/perovskite interfaces.¹⁰⁴⁴ Solution-processed BP quantum dots (BPQDs) with ambipolar conductivity were developed to be used as a dual-functional ESL material in plastic PSCs.¹¹¹⁷ BPQD-based ESL formed a cascade energy level for fast electron extraction and controlled the crystallization of the perovskite, thereby yielding compact high-quality (low-defect density) perovskite films with an ordered orientation.¹¹¹⁶

The resulting plastic planar PSCs exhibited an η value of 11.26%, owing to the efficient electron extraction and suppression of both radiative and trap-assisted nonradiative recombinations.¹¹¹⁶ More recently, phosphorene nanosheets, produced through vortex fluidic-mediated exfoliation under NIR pulsed laser irradiation, were also used as dopants for TiO_2 ETLs, resulting in low-temperature (100°C) processed, planar n-i-p PSCs with a maximum η value of 17.85%.¹¹²²

Tsikritzis *et al.* recently proposed a two-fold engineering approach for inverted PSCs, where ultrathin Bi_2Te_3 flakes were used (1) to dope the ETL and (2) to form a protective interlayer on top.¹¹²³ This approach improved the electron extraction rate, increasing the overall η by +6.6% compared to the reference cells. These effects were associated with an optimal alignment between the energy levels of the perovskite, cathode, and ETL. Furthermore, the interlayer of Bi_2Te_3 promoted efficient electron transport, while chemically protecting the underlying structure.¹¹²² By combining the two engineering approaches, the optimized PSCs reached an η value as high as 19.46%, while retaining more than 80% of their initial η value (after the burn-in phase) over 1100 h under continuous 1 sun illumination.¹¹²²

A complete replacement of the ETL with 2D materials was also presented for inverted planar PSCs by Castro *et al.* using functionalized GNRs.¹¹²⁴ Compared to PC_{61}BM , the functionalized nanoribbons were hydrophobic and exhibited higher LUMO energy levels, thus providing superior η and stability.¹¹²³

In addition, transition metal carbides, nitrides, and carbo-nitrides (*i.e.*, MXenes) have just started to be used for the design of high-performance ETLs.^{1125,1126} Ti_3C_2 MXenes have been used as the dopant for SnO_2 ETLs to improve the η value from 17.23% to 18.34%.¹¹²⁴ The superior performance recorded for MXene-incorporated SnO_2 -based PSCs was explained by both faster electron extraction and enhanced electrical conductivity compared to those exhibited in MXene-free ETLs.¹¹²⁴ Very recently, Agresti *et al.* used Ti_3C_2 MXene-based ETLs to improve PSCs using perovskite absorbers modified with MXenes.¹¹²⁵ The resulting cells exhibited a 26% increase in η and hysteresis reduction compared with the reference cells without MXenes.¹¹²⁵ Meanwhile, other less established 2D materials are also emerging as novel ETL material candidates. For example, Bi compounds, namely, $\text{Bi}_2\text{O}_2\text{Se}$ nanoflakes, have recently been used as hydrophobic and smooth ETLs to improve the electron collection/transport while promoting the formation of large perovskite crystals, achieving η value of up to 19.06%.¹¹²⁰ Metallic group-5 TMDs,



namely, 6R-TaS₂ flakes, were exfoliated and incorporated as a buffer layer in inverted PSCs to simultaneously enhance their η , lifetime, and thermal stability.¹¹²⁷ In detail, a thin buffer layer of 6R-TaS₂ flakes on top of the ETL facilitated electron extraction, allowing the device to reach the maximum η value of 18.45% (+12% vs. the reference cell).¹¹²⁶ In addition, stability tests using ISOS-L2, ISOS-D1, ISOS-D11, and ISOS-D2I protocols proved that the TaS₂ buffer layer retards the thermal degradation of PSCs, which retained more than 80% of their initial η over 330 h under continuous 1 sun illumination at 65 °C.¹¹²⁶

Table 10 summarizes the main results achieved by PSCs using ETLs based on GRMs.

6.2 Perovskite layers

Beyond optoelectronic properties, the key factors influencing the performance of a perovskite absorber are the morphology and grain size.^{1128–1130} Several works have highlighted the need to control the perovskite crystal morphology in order to obtain large grains that maximize charge photogeneration at the active layer.^{1128,1129,1131–1133} In fact, on one hand, an accurate control of the crystallization process is an essential step to improve the perovskite film morphology for correct device operation. On the other hand, the perovskite grain interfaces play a crucial role to influence charge transport and recombination phenomena. In this context, the incorporation of graphene derivatives into a perovskite layer seems a practicable way to improve the quality of perovskite layer morphology.¹¹³⁴ Hadadian *et al.* first reported the addition of N-doped reduced graphene oxide (N-RGO) into mixed organic–inorganic halide perovskites in order to increase the perovskite grain size.¹¹³⁵ This effect was tentatively attributed to the slowing down of the crystallization process.¹¹³⁵ Meanwhile, N-RGO decreased charge recombination owing to the surface passivation effect (Fig. 21a–e).¹¹³⁴ Therefore, the presence of N-RGO in the perovskite layer improved J_{SC} ($\sim 21 \text{ mA cm}^{-2}$), V_{OC} ($\sim 1.15 \text{ V}$), and FF ($\sim 0.73\%$), increasing η from 17.3% to 18.7%, compared to the reference PSC (Fig. 21f).¹¹³⁴ Alternatively, GO was used as both HTL and additive in the perovskite absorber in an inverted PSC.¹¹³⁶ The resulting PSC exhibited an η value as high as 15%, which was attributed to the hole acceptor role of GO in the hybrid GO:perovskite composite.¹¹³⁵ Moreover, the use of GQDs within the perovskite layer was reported as a promising strategy to passivate perovskite grain boundaries, improving the overall device performance.¹¹³⁷ In fact, conductive GQDs were used to facilitate electron extraction and simultaneously passivate dangling bonds and eliminate electron traps at the perovskite grain boundaries.¹¹³⁶ These effects enhanced the η value up to 17.6%.¹¹³⁶ Alternatively, 2D BP was proposed as an additive in the absorber precursor solution to obtain large ($> 500 \text{ nm}$) perovskite grains and to improve the η value up to 20.65%.¹¹³⁸

The enhanced PV performance was attributed to the improved charge extraction and transport of MAPbI₃ perovskite in the presence of BP nanosheets.¹¹³⁷ This approach was successfully applied to MAPbI₃-based n–i–p¹¹³⁷ and p–i–n configurations,¹¹³⁸ demonstrating the maximum η value of 20.65% and 20.0%, respectively.

Moreover, the BP-doped n–i–p PSCs presented excellent photostability under prolonged light soaking, preserving 94%

of the initial η after irradiation time of 1000 h,¹¹³⁷ while p–i–n PSCs have shown encouraging thermal stability, maintaining over 80% of their initial η value after aging for 100 h at 100 °C.¹¹³⁹ As a further demonstration of the emergent role of BP in PSCs, X. Gong and co-workers demonstrated the use of BPQDs as an additive for inorganic CsPbI₂Br perovskite films.¹¹⁴⁰ In that work, BPQDs were proposed as effective seed-like sites to modulate the nucleation and growth of CsPbI₂Br perovskite crystals, affording device η above 15%.¹¹³⁹ Despite these results, the instability of few-layer phosphorene under ambient conditions¹¹⁴¹ still represents a major concern hampering its massive use in PSCs.

In terms of the intrinsic stability of perovskites, Ag NP-anchored reduced graphene oxide (Ag-RGO) was used as an additive in perovskite films to suppress ion migration by improving the thermal and light stability.¹¹⁴²

Recently, Guo *et al.* used MXenes as a perovskite additive in mesoscopic PSCs.¹¹⁴³ In particular, the authors have shown that the termination groups of Ti₃C₂T_x can retard the perovskite crystallization rate, thereby increasing the perovskite crystal size.¹¹⁴² After optimization, a 12% enhancement in η compared to the reference PSCs was obtained with 0.03 wt% MXenes.¹¹⁴²

Agresti *et al.* used Ti₃C₂ MXenes as perovskite WF modifier to design n–i–p mesoscopic devices with η exceeding 20%.¹¹²⁵ Density functional theory calculations demonstrated that the formation of an interface dipole at the perovskite/Ti₃C₂T_x interface strongly depends on T_x terminations.¹¹²⁵ For example, in the case of OH-terminated MXene, a larger interface dipole than O terminations was demonstrated.¹¹²⁵ The overall reduction in perovskite WF upon MXene addition and the optimization of MXene-based ETL led to a 26% increase in η , together with hysteresis reduction, compared with the reference cells without MXenes.¹¹²⁵ The possibility to vary the MXene WF on demand and control the band-energy alignments with other layers forming an electronic device represents a winning strategy to enlarge the design parameter space and improve the device performance.

The attempt from Hu *et al.* toward stabilizing the α -phase of Cs_{0.1}FA_{0.9}PbI₃ perovskite by using 2D phenyl ethyl ammonium lead iodide ((PEA)₂PbI₄) nanosheets as the additive deserves a separate discussion, see Section 6.5.¹¹⁴⁴ Because of the 2D (PEA)₂PbI₄ nanosheets, the MA-free perovskite-based device reached a high η value of 20.44% and retained 82% of its initial efficiency after 800 h of continuous white light (1 sun) illumination.

Table 11 summarizes the main results achieved by PSCs integrating GRMs as perovskite additives.

6.3 HTLs and back electrodes

The main role of HTLs is to extract positive charges from the perovskite layer, by minimizing charge recombination losses, and to efficiently transport them at the corresponding current collector.^{1062,1063} Depending on the device's structure, HTLs have additional functions: in direct planar structures, HTLs also act as a perovskite protective layers against environmental factors (e.g., moisture and oxygen) and can even contribute to heat dissipation,^{1145,1146} improving the long-term stability of devices. In inverted planar structures, HTLs are often used as a scaffold layers for the growth of perovskites. Therefore, specific





Table 10 Summary of the PV performance of PSCs using ETLs based on GRMs^{a,b}

Material	Usage	Device structure	Cell performance				Ref.
			J_{sc} [mA cm ⁻²]	V_{oc} [V]	FF	η [%]	
Liquid phase exfoliated (LPE) graphene nanoflakes	Dopant for ETL	FTO/cTiO ₂ + G/mesoporous Al ₂ O ₃ /MAPbI ₃ (_{3-x})Cl _x /spiro-Au	21.9	1.04	0.73	15.5	1100
RGQ quantum dots (QD)	ETL (quasi-core-shell structure of ZnO-RGO QDs)	FTO/ZnO-RGO QD/MAPbI ₃ /spiro-OMeTAD/Au	21.7	1.03	0.68	15.2	1099
Graphene quantum dots (GQDs)	Interlayer at ETL/perovskite interface	FTO/cTiO ₂ /mTiO ₂ /GQDs/MAPbI ₃ /spiro-OMeTAD/Au	17.06	0.94	0.64	10.15	1101
Reduced-graphene scaffold (rGS)	Scaffold for perovskite growth	FTO/cTiO ₂ /rGS/MAPbI ₃ /spiro-OMeTAD/Au	22.8	1.05	0.72	17.2	1102
Graphene	Interlayer at front electrode/ETL interface	ITO-PET/graphene/ZnO-QDs/MAPbI ₃ /spiro-OMeTAD/Ag	16.8	0.94	0.62	9.73	1103
Graphene nanoflakes and GO-Li	Dopant for ETL; interlayer at ETL/perovskite interface	FTO/cTiO ₂ /mTiO ₂ :G/GO-Li/MAPbI ₃ /spiro-OMeTAD/Au	18.16 (50 cm ² active area)	8.57 (50 cm ² active area)	0.65 (50 cm ² active area)	12.6 (50 cm ² active area)	1107
RGQ	Dopant for ETL	FTO/cTiO ₂ /mTiO ₂ :RGO/(FAPbI ₃) _{0.85} (MAPbBr ₃) _{0.15} /spiro-OMeTAD/Au	21.98	1.11	0.8	19.54	1108
RGQ	RGQ grafted highly porous zinc stannate (Zn ₃ SnO ₄ -ZSO) scaffold nanofibers	(2) FTO/c-ZSO/RGO-ZSO _{0.7} /(FAPbI ₃) _{0.85} (MAPbBr ₃) _{0.15} /PTAA/Au	22.51	1.04	0.75	17.83	1110
Functionalized Graphene nanoribbon	ETL	Glass/ITO/PEDOT:PSS/MAPbI ₃ /functionalized-graphene nanoribbon	22.66	0.93	0.78	16.5	1123
Naphthalene diimide (NDAI)-graphene	ETL	ITO/NDI-Graphene:SnO ₂ /FA _{0.75} MA _{0.15} CS _{0.1} P-bI _{2.65} Br _{0.35} /spiro-OMeTAD/Au	22.66	1.084	0.82	20.16	1112
Graphene QD	Dopant for ETL	FTO/TiO ₂ /GQD/MAPbI ₃ /spiro-OMeTAD/Au	22.47	1.12	0.76	19.11	1109
GO and MoS ₂	Interlayer at HTL/perovskite interface; interlayer at ETL/perovskite interface	ITO/PEDOT:PSS/GO/MAPbI ₃ /PCBM/MoS ₂ /Ag	22.834	1.135	0.74	19.14	1163
GO	HTL and additive for perovskite	ITO/GO/MAPbI ₃ :GO/PCBM/Ag	20.71	0.96	0.76	15.2	1135
N-Doped graphene (NG)	Dopant for ETL	FTO/NiMgLiO/MAPbI ₃ /NG/PCBM/CQDs/Ag	19.68	1.07	0.75	15.57	1209
TiS ₂	ETL	FTO/TiS ₂ /perovskite/spiro-OMeTAD/Au	24.75	1.00	0.75	18.79	1114
TiS ₂	Interlayer at ETL/perovskite interface	ITO/SnO ₂ /TiS ₂ /perovskite/spiro-OMeTAD/Ag	24.57	1.11	0.79	21.73	1115
Black phosphorous quantum dots (BPDQs)	ETL	ITO/BPDQs/FA _{0.85} MA _{0.15} PbBr _{0.5} I _{2.5} /Spiro-OMeTAD/Au	16.77	1.03	0.65	11.26	1116
Phosphorene nanosheets	Dopant for ETL	FTO/(TiO ₂ :phosphorene)/FA _{0.8} MA _{0.2} PbBr _{0.5} I _{2.5} /Spiro-OMeTAD/Au	23.32	1.08	0.71	17.85	1124
Ti ₃ C ₂ (MXene)	Dopant for ETL	ITO/SnO ₂ -Ti ₃ C ₂ /perovskite/spiro-OMeTAD/Ag	23.14	1.06	0.75	18.34	1124
SnS ₂	ETL	ITO/SnS ₂ /perovskite/spiro-OMeTAD/Au	23.55	1.16	0.73	20.12	1044
Graphene ink	Dopant for ETL	ITO/SnO ₂ :G/perovskite/spiro-OMeTAD/Au	23.06	1.09	0.72	18.11	1111
Ti ₃ C ₂ (MXene)	ETL, interlayer at ETL/perovskite interface, dopant for perovskite	FTO/cTiO ₂ :MXenes/mTiO ₂ :MXenes/Mxenes/Cs ₂ (MA _{0.17} FA _{0.83})(1-x)Pb(I _{0.83} Br _{0.17}) ₃ :MXenes/spiro-OMeTAD/Au	23.82	1.09	0.78	20.14	675
Bi ₂ Te ₃	Dopant for ETL, interlayer at ETL/cathode interface	ITO/PTAA/(RbPbI ₃) _{0.04} (CsPbI ₃) _{0.95} [(FAPbI ₃) _{0.85} -(MAPbBr ₃) _{0.15}] _{0.91} /PCBM:Bi ₂ Te ₃ /BCP/Ag	22.52	1.096	0.788	19.46	1122
g-C ₃ N ₄	Interlayer at ETL/perovskite interface	FTO/SnO ₂ /g-C ₃ N ₄ /MAPbI ₃ /spiro-OMeTAD/Au	21.45	1.14	0.81	19.69	1113
Thiazole-modifiedg-C ₃ N ₄ nanosheets	Interlayer at ETL/cathode interface	ITO/PTAA/MAPbI ₃ /PC ₆₀ BM/thiazole-modifiedg-C ₃ N ₄ nanosheets/AZO/Ag	20.17	1.090	0.78	17.15	284
Sn ₂ :PCBM	ETL	ITO/NiOx/perovskite/PCBM-SnS ₂ /ZnO/Ag	22.70	1.06	0.83	19.95	1118
TiS ₂	Interlayer at ETL/perovskite interface	FTO/TiO ₂ nanograss/TiS ₂ /CS _{0.05} [MA _{0.13} FA _{0.87}] _{0.95} Pb(I _{0.87} Br _{0.13}) ₃ /spiro-OMeTAD/Au	22.05	1.13	0.725	18.73	1119
Ti ₃ C ₂ T _x	Dopant for ETL and additive for perovskite	ITO/NiO/MAPbI ₃ + MXenes/PCBM + MXenes/BCP/Ag	22.88	1.09	0.77	19.20	1120

Table 10 (continued)

Material	Usage	Device structure	Cell performance				Ref.
			J_{sc} [mA cm ⁻²]	V_{oc} [V]	FF	η [%]	
g-C ₃ N ₄ QDs	Dopant For ETL	ITO/g-C ₃ N ₄ QDs:SnO ₂ /Cs _x FA _y MA _z PbI ₃ /Spiro-OMeTAD/ Au	24.03	1.18	0.78	22.13	283
g-C ₃ N ₄ QDs	Interlayer at ETL/perovskite interface	FTO/SnO ₂ /g-C ₃ N ₄ QDs/Cs _q FA _w MA _k PbI _x Br _y Cl _z / Spiro-OMeTAD/Au	23.41	1.13	0.77	20.30	285
Bi ₂ O ₃ Se nanoflakes	ETL	ITO/Bi ₂ O ₃ Se/MAPbI ₃ /Spiro-OMeTAD/MoO _x /Ag	16.16	0.99	0.57	9.12	1121
SnO ₂ /Bi ₂ O ₃ Se nanoflakes	ETL	ITO/SnO ₂ /2D Bi ₂ O ₃ Se/MAPbI ₃ /MoOx/Ag	23.48	1.07	0.76	19.06	1120
6R-TaS ₂	Interlayer at ETL/cathode interface	ITO/PTAA//((RbPbI ₃) _{0.04} (CsPbI ₃) _{0.03} [(FAPbI ₃) _{0.85} - (MAPbBr ₃) _{0.15}] _{0.91} /PC ₇₀ BM/TaS ₂ /BCP/Ag	21.45	1.08	0.796	18.45	1126

^a MA = CH₃NH₃, ^b FA = HC(NH₂)₂.

morphology and structural properties are required, especially for low-temperature solution-processed device fabrication on flexible substrates.¹¹⁴⁷ Moreover, because in such a configuration, sunlight comes from the p-type electrode, HTLs must be thin to prevent optical losses, while impeding short-circuiting between the conductive oxide (FTO or ITO for rigid and flexible substrates, respectively) and perovskite active layer.^{1148–1150} In addition, the HTLs need to ensure efficient hole transport toward the electrode by minimizing the series resistance, as well as charge recombination processes.^{1147–1149}

Finally, HTL-covered substrates should exhibit optimal wettability and compatibility with the solvent used for the perovskite deposition step. In this context, PEDOT:PSS has been the most frequently used HTL material in inverted PSCs, due to the following properties: (1) energy-level (HOMO level at 5.25 eV)¹¹⁵¹ matching with ITO ϕ_w (4.9 eV)¹¹⁵² and perovskite HOMO level (5.4 eV);¹¹⁵³ (2) excellent μ ; (3) simple solution processability.¹¹⁵⁴ The doping with GRMs has been used to improve the physical, mechanical, and electrical features of PEDOT:PSS. For example, RGO was added into PEDOT:PSS.^{1155,1156} An η improvement of $\sim 22\%$ was observed in RGO-doped PEDOT:PSS (RGO:PEDOT:PSS)-based device compared to the nondoped HTL-based reference due to the suppression of leakage current.¹¹⁵⁵ Giuri and co-workers investigated the cooperative effect of GO and glucose inclusion in the PEDOT:PSS matrix.¹¹⁵⁷ Chemically functionalized GO with the glucose molecule was used to modify the chemical properties of the PEDOT:PSS surface, changing the wettability, as well as improving the electrical conductivity of PEDOT:PSS.¹¹⁵⁶ Concurrently, glucose molecules favored the reduction of GO¹¹⁵⁸ and enhanced the wettability of the PEDOT:PSS substrate due to the presence of numerous hydroxyl terminations. Consequently, the GO-doped glucose/PEDOT:PSS HTL increased the V_{oc} value compared to the PEDOT:PSS-based devices, indicating minimal losses, high hole selectivity, and reduced trap density at the optimized HTL/perovskite coverage.¹¹⁵⁶ The use of a chemical approach to control the optical and electrical properties of GO was also reported by Liu *et al.*, who used silver trifluoromethanesulfonate (AgOTf) as an inorganic dopant for single-layer GO.¹¹⁵⁹ In particular, the spin coating of AgOTf in a nitromethane solution over a GO-doped PEDOT:PSS layer allowed the HTL ϕ_w to be finely tuned, thus lowering the energy barrier for hole transfer at the PEDOT:PSS:AgOTf-doped GO/perovskite interface.¹¹⁵⁸ This effect led to an η improvement for both flexible and rigid PSCs in comparison to the reference devices based on PEDOT:PSS.

Li *et al.* demonstrated that GO can also be used as an efficient interlayer between the conductive layer and PEDOT:PSS HTL.¹¹⁶⁰ In fact, the high conductivity of PEDOT:PSS combined with the electron-blocking capability of GO suppressed current leakage in the PSC structure, while improving the carrier injection and perovskite film morphology.¹¹⁵⁹ The as-realized device has shown a maximum η value of 13.1%, which was higher than that reached by the reference PSC based on PEDOT:PSS ($\eta = 10\%$).¹¹⁵⁹

The insertion of a buffer layer between ITO and PEDOT:PSS has been demonstrated to significantly increase the long-term stability of nonencapsulated devices under atmospheric conditions



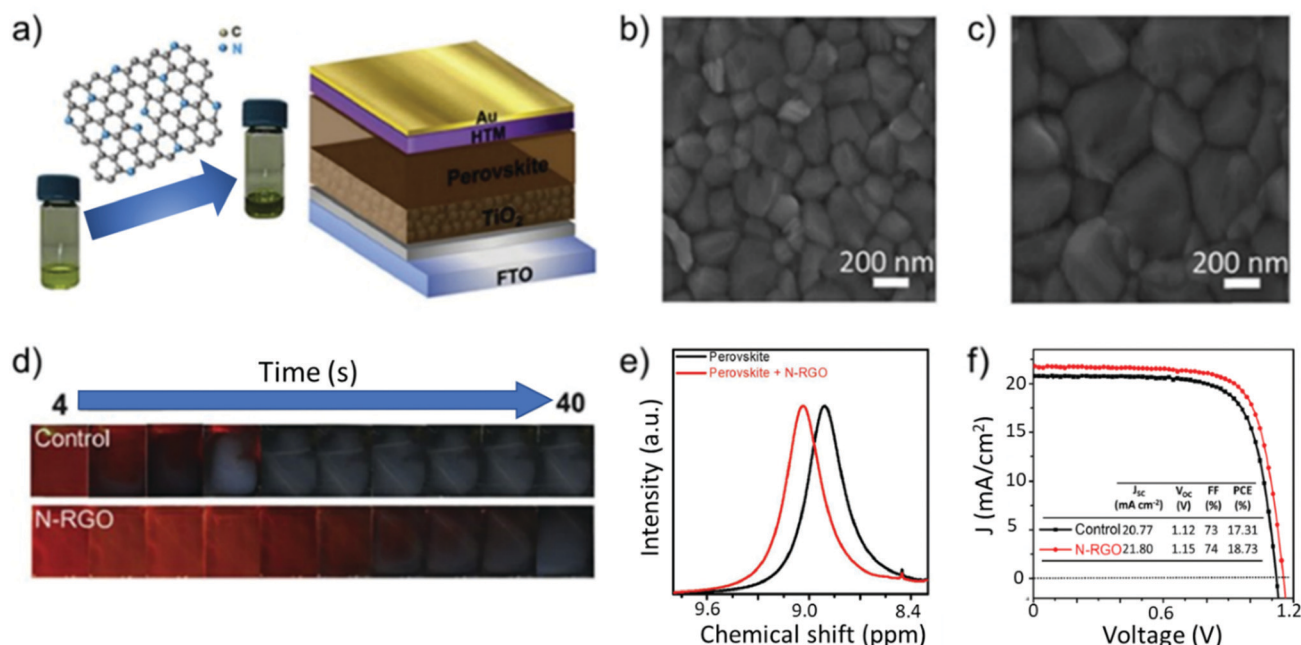


Fig. 21 (a) Schematic showing the N-RGO-doped perovskite solution and PSC with a structure of FTO/TiO₂/N-RGO/perovskite/spiro-OMeTAD/Au. (b and c) SEM images of perovskite films before and after the incorporation of N-RGO. (d) Photographs of perovskite films during the annealing process at 100 °C. (e) ¹H NMR spectra of perovskite and N-RGO/perovskite solution. (f) *J*–*V* characteristics of the control device and N-RGO-incorporated device. Adapted from ref. 1134.

Table 11 Summary of the PV performance of PSCs incorporating GRMs in the perovskite active layer^{ab}

			Cell performance				
Material	Usage	Device structure	J_{sc} [mA cm ⁻²]	V_{OC} [V]	FF	η [%]	Ref.
N-Doped RGO nanosheets	Additive in perovskite	(FTO)/cTiO ₂ /mTiO ₂ /FA _{0.85} MA _{0.15} Pb(I _{0.85} Br _{0.15}) ₃ /spiro-OMeTAD/Au	21.8	1.15	0.74	18.73	1134
Graphene quantum dots (GQDs)	Additive for perovskite	FTO/cTiO ₂ /mTiO ₂ /MAPbI ₃ /spiro-OMeTAD/Au	22.91	1.05	0.76	18.34	1136
2D BP	Additive for perovskite	FTO/cTiO ₂ /SnO ₂ /perovskite:2D BP/Spiro-OMeTAD/Ag,	1.82	23.31	0.82	20.65	1137
Silver nanoparticle-anchored reduced graphene oxide (Ag-rGO)	Additive in perovskite	FTO/bl-TiO ₂ / <i>m</i> -TiO ₂ /Al ₂ O ₃ /MAPbI _{3-<i>x</i>} Cl _{<i>x</i>} /Ag-rGO/spiro-OMeTAD/Au	0.929	23.501	0.74	16.101	1141
Ti ₃ C ₂ MXenes	Additive in perovskite	FTO/SnO ₂ /MAPbI ₃ :MXenes/spiro-OMeTAD/Au	1.03	22.26	0.76	17.41	1142
Ti ₃ C ₂ (MXene)	ETL, interlayer at ETL/perovskite, additive in perovskite	FTO/cTiO ₂ :MXenes/mTiO ₂ :MXenes/Mxenes/Cs _{<i>x</i>} (MA _{0.17} FA _{0.83})(1- <i>x</i>)Pb(I _{0.83} Br _{0.17}) ₃ :MXenes/spiro-OMeTAD/Au	1.09	23.82	0.78	20.14	675
Black phosphorus quantum dots (BPQDs)	Additive in perovskite	ITO/PTAA/MAPbI ₃ -BPQDs/PCBM/BCP/Ag	21.9	1.10	0.83	20.0	1138
BPQDs	Additive in perovskite	FTO/SnO ₂ /BPQDs + CsPbI ₂ Br/spiro-OMeTAD/Au	15.86	1.25	0.78	15.47	1139
2D (PEA) ₂ PbI ₄ nanosheets	Additive in perovskite	FTO/cTiO ₂ /mTiO ₂ /Cs _{0.1} FA _{0.9} PbI ₃ + 2D (PEA) ₂ PbI ₄ /spiro-OMeTAD/Au	24.8	1.05	0.78	20.27	1143
g-C ₃ N ₄	Additive in perovskite	FTO/cTiO ₂ /MAPbI ₃ :g-C ₃ N ₄ /spiro-OMeTAD/Au	24.31	1.07	0.74	19.49	282

^a MA = CH₃NH₃. ^b FA = HC(NH₂)₂.

(temperature of 21–24 °C and humidity of 38–55%).¹⁰⁵⁸ In fact, the GO buffer layer can prohibit direct contact between the ITO and highly acidic PEDOT:PSS by slowing down photoelectrode degradation.¹⁰⁵⁸ The improved η and stability achieved with 2D interlayers was clearly demonstrated by Kakavelakis and co-workers, who used a MoS₂ interlayer between PTAA (HTL) and perovskite.¹⁰³⁹ The introduction of MoS₂ flakes afforded a device with an η value of 16.42% and a prolonged lifetime,

corresponding to an 80% retention of their initial performance after 568 h of continuous illumination.¹⁰³⁹ By following this approach, Tang and co-workers demonstrated planar inverted PSCs with the glass/ITO/PTAA/MoS₂/perovskite/PCBM/BCP/Ag structure exceeding η of 20%.¹¹⁶¹ In this case, the in-plane coupling between epitaxially grown CH₃NH₃PbI₃ and MoS₂ crystal lattices led to perovskite films with a large grain size, low trap density, and preferential growth orientation along the



(110) direction normal to the MoS₂ surface. Very recently, Zhang *et al.* replaced the MoS₂ interlayer with 2D antimonene.¹¹⁶² This new 2D material exhibits a thickness-dependent bandgap that can be advantageous in PV and other optoelectronic devices.¹¹⁶¹ In particular, antimonene-based PSCs displayed an outstanding η value of 20.11% with a remarkable V_{OC} value of 1.114 V, while the reference device has shown an η value of 17.60% with a V_{OC} value of 1.065 V.¹¹⁶¹ Antimonene provided sufficient nucleation sites, promoting perovskite crystallization and therefore speeding-up hole extraction at the photoelectrode.¹¹⁶¹

Moreover, Cao *et al.* proposed the use of WS₂ flakes as an efficient interlayer at the PTAA/perovskite interface, acting as a template for the van der Waals epitaxial growth of mixed perovskite films.¹¹⁶³ The WS₂/perovskite heterojunction has shown an engineered energy alignment, boosting charge extraction and reducing interfacial recombination.¹¹⁶² Inverted PSCs with WS₂ interlayers reached η values up to 21.1%, which is among the highest value reported for inverted planar PSCs.¹¹⁶² A further evolution in the use of 2D interlayers for planar PSCs was proposed by Wang and co-workers using a double interlayer approach: GO was used at the interface between PEDOT:PSS and perovskite, while MoS₂ was used at the interface between PCBM and the Ag electrode.¹¹⁶⁴ The PSC with GO and MoS₂ layers has shown an increase in V_{OC} from 0.962 to 1.135 V, and η from 14.15% to 19.14%.¹¹⁶³ However, despite the extensive use of PEDOT:PSS in PSCs, PEDOT:PSS suffers from hygroscopicity and acidic properties, which cause faster degradation of both organic layers and organo-lead halide perovskites layer.¹¹⁶⁵ Thus, several efforts have been made in order to replace PEDOT:PSS with the most stable HTL based on graphene or other 2D materials, including TMDs.^{1166,1167} In fact, the lone pair of electrons of the carbon and chalcogen atoms in the structure of graphene (and derivative) and TMDs, respectively, improves the μ value of HTL, due to the demonstrated ballistic transport.^{1168–1170} Moreover, chemical doping and simple surface treatment allow the easy modulation of the energy levels of both (R)GO^{1171,1172} and TMD films.^{1173,1174} For example, Kim and co-workers demonstrated the feasibility to replace PEDOT:PSS with polycrystalline structure of MoS₂ and WS₂ layers, which were synthesized through a chemical deposition method.¹¹⁵⁰ The devices with a planar inverted architecture of ITO/MoS₂ or WS₂/perovskite/PCBM/BCO/LiF/Al exhibited η of 9.53% and 8.02% for MoS₂ and WS₂ cases, respectively, comparable to that measured for PEDOT:PSS-based devices (9.93%).¹¹⁵⁰ In the same work, the use of GO as the HTL resulted in an η of 9.62%, demonstrating the effectiveness of GRMs in PSCs.¹¹⁵⁰ The use of TMDs for HTL in inverted PSCs has been recently optimized by Huang and co-workers, who achieved an η of 14.35% and 15.00% for MoS₂- and WS₂-based PSCs, also demonstrating enhanced stability compared to the PEDOT:PSS-based reference devices.¹¹⁷⁵

Following the aforementioned studies, GO and RGO in both pristine and functionalized forms have been extensively tested as HTLs, yielding valuable results in terms of η and stability. For example, Wu *et al.* improved the η of ITO/HTL/CH₃NH₃PbI_{3-x}Cl_x/PCBM/ZnO/Al PSCs from 9.2% to 12.4% by replacing PEDOT:PSS with a GO layer.¹⁰⁵⁰ In particular, by tuning the concentrations of GO in neutral aqueous suspensions from 0.25 mg mL⁻¹ to

4 mg mL⁻¹, the authors were able to deposit a GO layer with a thickness in the range of ~2–20 nm, finely controlling the PV performance of the devices.¹⁰⁵⁰

More recently, GO has been exploited as the HTM even in the form of nitrogen-doped nanoribbons (NGONRs) by Kim and co-workers.¹¹⁷⁶ The NGONRs were synthesized starting from MWCNTs and subsequently doped by pyrolyzing nanoribbons/polyaniline (PANI) composites at 900 °C for 1 h in an Ar atmosphere.¹¹⁷⁵ Different from the case of PEDOT:PSS, the deposition of perovskite films onto NGONRs allowed the perovskite film to grow into large textured domains, yielding an almost complete coverage.¹¹⁷⁵ Thus, small-area devices reached an η value of 12.41%, which was higher than that of the PEDOT:PSS-based reference (9.70%).¹¹⁷⁵ Notably, NGONR-based cells demonstrated negligible current hysteresis along with improved stability under ambient conditions (average temperature and humidity of 20 °C and 47%, respectively), since the absence of the PEDOT:PSS layer prevented perovskite degradation caused by the acidic nature of the polymer.¹¹⁷⁵ A significant η of 16.5% and extraordinary stability was also achieved by using GO as the HTL in an inverted PSC.¹¹⁷⁷ Long-term aging test under ambient humidity with a relative humidity of 60% was carried out on the encapsulated devices.¹¹⁷⁶ After initial *J*-*V* measurements, the devices were continuously illuminated and then stored in the dark under standard laboratory conditions.¹¹⁷⁶ The GO-based devices reported long-term stability compared to PEDOT:PSS-based PSCs.¹¹⁷⁶ In particular, their η decreased by only 10% after nearly 2000 h.¹¹⁷⁶

The improvement in device stability was demonstrated using a RGO nanosheet as the HTL in the inverted structure of ITO/RGO/perovskite/PCBM/BCP/Ag.¹⁰⁴⁹ The RGO/perovskite junction induced faster charge transfer across its interface, resulting in reduced charge recombination compared to the PEDOT:PSS-based PSCs.¹⁰⁴⁹ Furthermore, the perovskite grains (100–200 nm grains) of the perovskite film grown on the RGO layer reduced the total number of grain boundaries, increasing the cell FF, compared to the PEDOT:PSS-based reference (perovskite with grain size of <100 nm).¹⁰⁴⁹ RGO-based devices have shown promising stability, retaining 62% of the initial η even after 140 h of light exposure, while PEDOT:PSS-based devices failed.¹⁰⁴⁹ The stability of cells with RGO stemmed from the quasi-neutral properties of RGO with few surface oxygen functionalities and the inherent passivation ability of RGO against moisture and oxygen.¹⁰⁴⁹ With the aim to further enhance the stability of PEDOT:PSS-based inverted PSCs, GO¹¹⁷⁸ and ammonia-modified GO (GO:NH₃)¹¹⁷⁹ were reported as efficient interlayers between the HTL and perovskite active layer. In the latter case, a thin GO:NH₃ layer of ~2 nm was spin coated onto the PEDOT:PSS surface and subsequently annealed at 120 °C for 10 min.¹¹⁷⁸ Similar to the results reported using the RGO nanosheet,¹⁰⁴⁹ the perovskite film realized onto the PEDOT:PSS/GO:NH₃ substrate displayed improved crystallization with a preferred orientation order and nearly complete coverage, improving its optical absorption.¹¹⁷⁸ Furthermore, the optimal energy-level matching between the PEDOT:PSS-GO:NH₃ HTL and perovskite led to an η value up to 16.11%, which was significantly superior compared to the values measured for bare



PEDOT:PSS-based PSCs ($\eta = 12.5\%$).¹¹⁷⁸ Notably, the highly ordered perovskite structure led to a marked improvement in the structural stability of the active film, extending the device lifetime in ambient conditions.¹¹⁷⁸ Organo-sulfonate graphene (oxo-G) was reported to replace PEDOT:PSS in inverted PSCs, significantly enlarging the device's lifetime.¹¹⁸⁰ In fact, the use of oxo-G as the HTL effectively prevented the access of water vapor into the device stack, without penalizing the overall η of the devices, which reached valuable η of 15.6%.¹¹⁷⁹ Noteworthy, the unencapsulated devices retained $\sim 60\%$ of the initial η after ~ 1000 h light soaking under 0.5 sun and ambient condition.¹¹⁷⁹ The obtained results confirmed the use of functionalized graphene-based materials as a viable route to stabilize inverted PSCs.¹¹⁷⁹

In the archetypical mesoscopic structure of $\text{cTiO}_2/\text{mTiO}_2$ (or Al_2O_3)/perovskite/spiro-OMeTAD/Au, GRMs have been widely used to replace traditional HTMs, as well as interlayers, mainly aiming to solve certain issues related to the spiro-OMeTAD HTL, such as instability and high cost ($\$170\text{--}475/\text{g}$).¹¹⁸¹ In particular, spiro-OMeTAD needs to be doped to increase the intrinsic low electrical conductivity of its pristine amorphous form.¹¹⁸² To this end, lithium bis(trifluoromethanesulfonyl)imide (Li-TFSI)^{1183,1184} and tert-butylpyridine (TBP)¹¹⁸⁵ are the most frequently used dopants to increase μ_{h} and to improve contact at the spiro-OMeTAD/perovskite interface, respectively. However, major instability drawbacks must be considered when the aforementioned dopants are used. In fact, Li-TFSI exposed to ambient conditions is deliquescent¹¹⁸⁶ and tends to dissociate from the spiro-OMeTAD, negatively affecting its performances.¹¹⁸⁵ In addition, TBP corrodes the perovskite layer due to its polar nature.¹¹⁸⁷

With the aim to replace common dopants of the spiro-OMeTAD layer, Luo and co-authors recently proposed the use of GO reduced by a ferrous iodide acidic solution as an alternative HTM dopant.¹¹⁸⁸ The devices prepared using iodine-RGO/spiro-OMeTAD HTL displayed an η of 10.6%, which was lower compared to that of doped spiro-OMeTAD-based devices (13.01%).¹¹⁸⁷ However, the cell stability was significantly improved.¹¹⁸⁷ In particular, the η value of the RGO-based devices retained above 85% of the initial value even after 500 h of storage in air, while the η value of

the device fabricated with doped spiro-OMeTAD decreased to 35% under the same aging conditions.¹¹⁸⁷

An alternative strategy to enhance cell η by preventing perovskite/spiro-OMeTAD interface degradation involves the use of an interfacial layer based on 2D materials. As a recent example, phosphorene has been used at both mTiO_2 /perovskite and perovskite/spiro-OMeTAD interfaces in mesoscopic n-i-p PSCs, achieving a remarkable η of 19.83%.

Solution-processed phosphorene has shown ambipolar carrier transport behavior and can be considered as a viable route for enabling great advances in PSC performance *via* judicious interfacial positioning of phosphorene in the cell structure.¹¹⁸⁹ Regarding the perovskite/spiro-OMeTAD interface stability, Capasso *et al.* showed that the insertion of few-layers MoS_2 retarded PSC degradation with higher lifetime stability, of over 550 h, compared to the reference MoS_2 -free PSC ($\Delta\eta/\eta = -7\%$ *vs.* $\Delta\eta/\eta = -34\%$).¹¹⁹⁰ The authors justified the extended lifetime to the role of MoS_2 flakes that act as a protective layer, preventing the formation of shunt contacts between the perovskite and Au electrode.¹¹⁸⁹ The enhanced stability of the mesoscopic device using an MoS_2 interlayer was recently demonstrated even under prolonged light soaking condition at 1 sun illumination.^{1105,1191} However, the MoS_2 VB does not perfectly match with the perovskite HOMO level, possibly forming an energy barrier for the hole extraction process that causes V_{OC} reduction. In order to fully exploit the potential of MoS_2 as an interlayer, Najafi *et al.* produced MoS_2 quantum dots (MoS_2 QDs), derived by LPE-produced MoS_2 flakes and hybridized with functionalized reduced graphene oxide (f-RGO), to provide both hole extraction and electron blocking properties (Fig. 22).¹¹⁹² In fact, the intrinsic n-type doping of the MoS_2 flakes introduce intraband gap states that can extract holes through an electron injection mechanism.¹¹⁹¹ Meanwhile, quantum confinement effects increase the E_{g} of MoS_2 (from 1.4 eV for flakes to more than 3.2 eV for QDs), rising its CB minimum energy from -4.3 eV to -2.2 eV. The latter value is above the CB of $\text{CH}_3\text{NH}_3\text{PbI}_3$. Therefore MoS_2 QDs exhibit electron-blocking properties.¹¹⁹¹ In addition, the hybridization of MoS_2 QDs with f-RGO, obtained by chemical silanization-induced linkage between RGO and (3-mercaptopropyl)trimethoxysilane, promoting the deposition of a homogeneous interlayer onto the

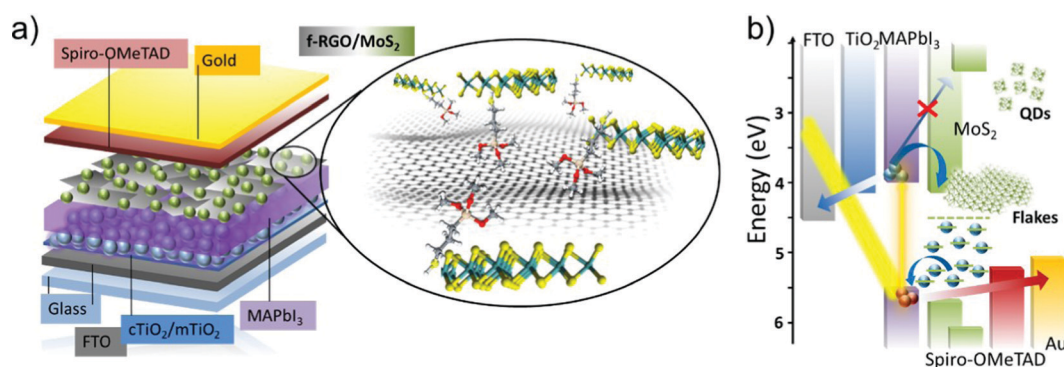


Fig. 22 (a) Schematic of mesoscopic MAPbI_3 -based PSC using MoS_2 QDs:f-RGO hybrids as both HTL and active buffer layer. (b) Schematic of the energy band edge positions of the materials used in different components of the assembled mesoscopic MAPbI_3 -based PSCs. Reprinted with permission from ref. 1191, Copyright 2018, American Chemical Society.



perovskite film.¹¹⁹¹ In fact, the f-RGO flakes plug the pinholes of MoS₂ QD films.¹¹⁹¹ The as-prepared PSCs achieved η values of up to 20.12% (average η of 18.8%).¹¹⁹¹ As an alternative to MoS₂ QDs, Agresti *et al.* proposed a chemical functionalization of the MoS₂ flakes (fMoS₂), by linking a thiol group of 3-mercaptopropionic acid (MPA) moieties to the MoS₂ surface *via* S-S van der Waals physisorption and/or S-vacancy passivation (Fig. 23).¹¹⁹³ Apart from chemically and electronically repairing the defective lattice of the MoS₂ flakes, MPA-based functionalization is effective to upshift the MoS₂ energy bands.¹¹⁹² The upshift of the MoS₂ energy bands aligns the VB edge of MoS₂ with the HOMO level of the perovskite, improving the hole extraction process.¹¹⁹² In addition, the MPA-based functionalization shifts the CB edge of MoS₂ above the LUMO level of the perovskite, hindering undesired electron transfer (*i.e.*, providing electron blocking properties).¹¹⁹² Owing to these effects, the MPA-based functionalization of MoS₂ flakes, when integrated in PSCs, improved the η value of the reference devices without MoS₂-based interlayer by +11.6%.¹¹⁹²

Recently, another mechanism has been proposed by Shi *et al.* to explain the hole extraction properties of 2D MoS₂.¹¹⁹⁴ This mechanism relies on the presence of intrinsic S vacancies at the MoS₂ edges that stabilize halide vacancies at the perovskite/MoS₂ interface.¹¹⁹³ This process induces an interface dipole moment, which reverses the offset of the VB maxima.¹¹⁹³ Overall, this effect can lead to an ultrafast (picosecond timescale) hole transport from the perovskite to the current collector, boosting the performance of MoS₂ HTL-based PSCs.

Beyond MoS₂, both GO¹¹⁹⁵ and functionalized GO (fGO)¹¹⁹⁶ were used as an efficient buffer layer at the perovskite/spiro-OMeTAD interface. In particular, when GO was deposited onto the perovskite surface, it performed as a base that absorbed spiro-OMeTAD onto its surface.¹¹⁹⁴ Moreover, parts of the O atoms in GO were demonstrated to connect with unsaturated Pb atoms in the perovskite, improving adhesion between spiro-OMeTAD and the active layer.¹¹⁹⁴ Furthermore, the surface defect states of the perovskite were dramatically reduced, leading to an η increase of 45.5%, from 10.0% in the case of a standard PSC structure to 14.5% when GO was inserted as the interlayer.¹¹⁹⁴

Amino-functionalized N-doped graphene (NG) was tested as an interlayer between perovskite and undoped spiro-OMeTAD in the standard mesoscopic structure (FTO/cTiO₂/mTiO₂/perovskite/dopant-free spiro-OMeTAD/Au), reaching higher η (14.6%) compared to the reference device (η = 10.7%).¹¹⁹⁵ These results were explained by the absorption of spiro-OMeTAD from NG-treated perovskite surface *via* π - π interactions, ensuring electron-rich molecules. In fact, N atoms interact with undercoordinated Pb₂⁺ ions by donating electron density.¹¹⁹⁵ Thus, the perovskite surface is passivated and the charge extraction toward the HTL is optimized.^{1195,1197} Consequently, η enhancement was associated with the increase in J_{SC} and FF due to reduced charge recombination at the perovskite/HTM interface.¹¹⁹⁵ Functionalized RGO was also used at the perovskite/spiro-OMeTAD interface in the planar configuration to reduce interfacial recombination and enhance hole extraction.¹¹⁹⁸ An alternative strategy to

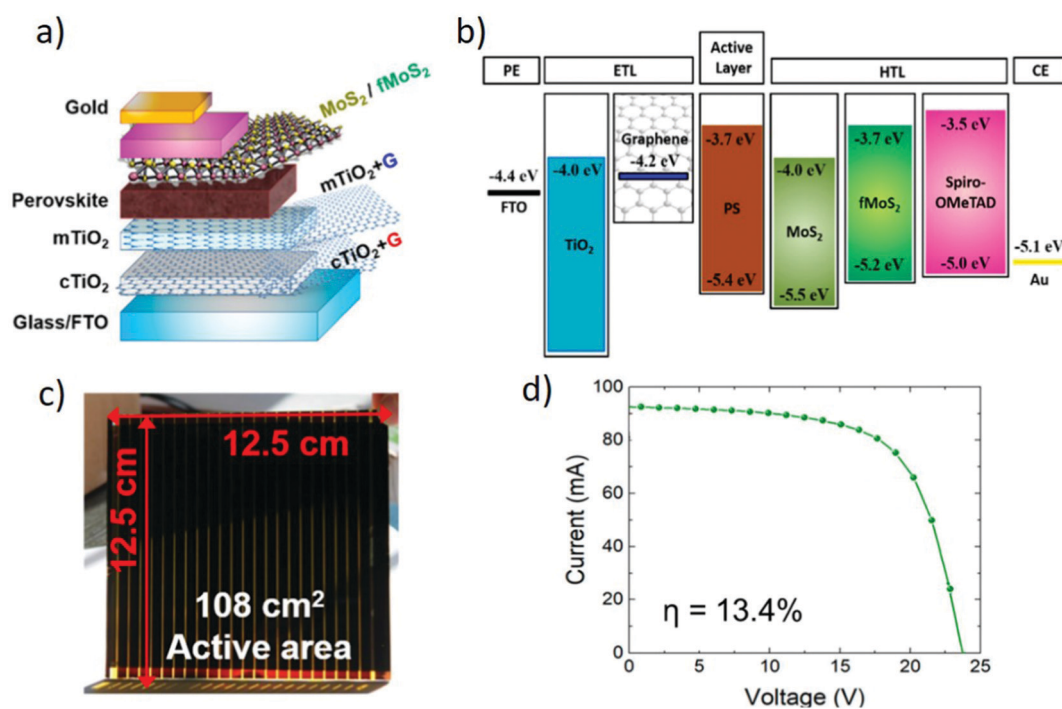


Fig. 23 (a) Engineered PSC architecture using chemically functionalized molybdenum disulfide (fMoS₂) as the interlayer at the perovskite/HTL interface for improving the hole injection/collection at the CE and (b) its energy band diagram. (c) Photograph of a representative large-area PSM (108 cm² active area, 156.25 cm² substrate area), showing an η value of 13.4% under 1 sun illumination, as shown by (d) its J - V characteristic. Adapted with permission from ref. 1192, Copyright 2019, American Chemical Society.



replace spiro-OMeTAD is to use more stable and dopant-free HTMs. To this end, Nouri *et al.* demonstrated that the use of copper phthalocyanine (CPC) as an alternative HTM can produce valuable η only if an interlayer of GO was used between the perovskite and HTL.¹¹⁹⁹ In a recent work, You *et al.* proposed the use of solution-processed high-mobility 2D materials, namely, MoS₂ and BP, to conduct holes from the grain boundary of the perovskite layer to the HTL, proposing a novel strategy to passivate defects in PSC grain boundaries.¹²⁰⁰

An attempt to replace spiro-OMeTAD with sprayed RGO was reported by Palma *et al.*¹⁰⁵² Despite the η values of RGO-based PSCs ($\eta = 5\%$) were lower than that obtained with devices based on doped spiro-OMeTAD as the HTL ($\eta = 11\%$), the authors have reported an impressive improvement in device stability.¹⁰⁵² In fact, PSC stability was demonstrated in an endurance test carried out under both shelf-life conditions (in air, in dark, at ambient temperature (RT = 23 °C) and relative humidity (RH = 50%)) and open-circuit load conditions for prolonged light-soaking stress test (1 sun at 65 °C and ambient RH).¹⁰⁵² In particular, 1987 h of shelf-life testing revealed that η increased by more than 30% in RGO-based-PSCs, while spiro-OMETAD-based PSCs evidenced a drastic η reduction (−44%).¹⁰⁵² Notably, the consecutive light-soaking tests induced a further η decrease of only 26% in RGO-based PSCs, while spiro-OMeTAD-based device completely failed the test.¹⁰⁵²

RGO was also used as a dopant for poly-3(hexylthiophene) (P3HT) polymer, a valid HTM alternative to spiro-OMeTAD when doped with LiTFSI salts and TBP.¹²⁰¹ The enhanced η (~9%) of PSC using RGO-doped P3HT compared to devices using bare P3HT (6.5%) was complemented by improved shelf-life stability.¹²⁰⁰ The authors demonstrated that RGO doping introduced additional charge percolation pathways in P3HT and enhanced the interfacial contacts with the underlying perovskite layer and Au back electrode.¹²⁰⁰ Thus, improved hole depletion from the perovskite layer limits charge recombination effects by avoiding trapped charges at the perovskite/HTM interface.¹²⁰² The increase in μ_h of P3HT was reported as the key point to improve the PSC performance by Ye and co-workers, who proposed an imidazole-functionalized GO (IGO) as the HTL dopant.¹⁰⁵³ PSCs using IGO-doped P3HT achieved an η value of 13.82%, which was among the highest reported for P3HT-based PSCs.¹⁰⁵³ Apart from the increase in μ_h , IGO doping allowed the P3HT HOMO level to be shifted from −5.0 eV to −5.2 eV.¹⁰⁵³ Moreover, the hydrophobicity of the P3HT/graphene layer resulted in excellent stability of the PSCs, which retained more than 70% of their initial performance after 8 weeks of storage in ambient conditions (25 °C, 20–40% RH).¹⁰⁵³

The hydrophobicity of GRMs is a peculiar property that drives their exploitation in the development of new and more robust HTMs and/or protecting layers for PSCs. Very recently, Cao and co-workers successfully replaced spiro-OMeTAD with a perthiolated tri-sulfur-annulated hexa-peri-hexabenzocoronene (TSHBC)/graphene layer, achieving an η value exceeding 14% on small-area devices.¹⁰⁵⁵ Such a tested compound combined the hydrophobicity of both graphenes and thiols, providing an

effective molecular sealing approach to improve the stability of complete devices.¹⁰⁵⁵ Moreover, the TSHBC/graphene layer exhibited an excellent hole extraction capability, ensuing from the Pb–S coordination bond between TSHBC and perovskite, together with enhanced μ_h due to the presence of GNSs in the HTL.¹⁰⁵⁵ A similar approach was also reported by Wang and co-authors that used a multilayered buffer layer with the aim to replace spiro-OMeTAD and to protect perovskite from moisture.¹⁰⁵⁶ The realized SWNT/GO/polymethyl methacrylate (PMMA) layer conjugated the SWNT capability in assisting photogenerated carrier extraction/transport with the electron blocking property of GO.¹⁰⁵⁶ Moreover, the built-in potential across the device drastically increased upon the insertion of the GO layer, which prevented carrier recombination losses.¹⁰⁵⁶ With regard to stability, the η of spiro-OMeTAD-based PSC significantly reduced from 10.5% to 5.8% during a ten-day test, while the SWNT/GO/PMMA-based cells exhibited stable performance, showing a decrease of η from 10.5% to 10.0% in the same timeframe.¹⁰⁵⁶ This result was attributed to the PMMA layer, which acts as an effective barrier to moisture and oxygen penetration, preventing the degradation of the perovskite layer.¹⁰⁵⁶ We should mention that HTM doping was also realized using 2D materials other than GO.¹²⁰³ Indeed, effective HTMs were produced by means of BP,^{1204,1205} graphene,¹²⁰⁶ and functionalized MoS₂¹²⁰⁷ dopants. For example, BP/spiro-OMeTAD blend-based PSCs have shown a remarkable increase in η (more than 20%) compared to PSCs without BP.¹²⁰³ Lastly, solution-processed 2D-conjugated polymers have also been proposed as effective dopant-free HTL materials alternative to spiro-OMeTAD, confirming that the design of novel 2D materials can prospectively offer advanced strategies to further boost the η and the stability of PSCs.¹²⁰⁸ In detail, planar n–i–p-structured PSCs based on 2DP-TDB as a dopant-free HTM recently achieved champion η as high as 22.17%, while showing improved stability under continuous light soaking in an inert atmosphere compared to control devices.¹²⁰⁷

Recently, graphene-based dopants for HTLs have been demonstrated to have a crucial role in CE replacement.¹²⁰⁹ In fact, one of the main hurdles of PSC technology is that the hole transporting materials established for state-of-the art Au-based devices are not compatible with carbon pastes used for the fabrication of carbon-based PSCs. Thus, Chu *et al.* proposed the use of HTL based on solution-processed P3HT/graphene composites, exhibiting outstanding μ_h and thermal tolerance.¹²⁰⁸ In fact, after annealing at 100 °C, the μ_h value of this HTL increased from 8.3×10^{-3} to 1.2×10^{-2} cm² V^{−1} s^{−1}, which was two orders of magnitude larger than that of pure P3HT.¹²⁰⁸ As a result, the authors reported carbon-based PSCs with a record η value of 17.8% (certified by Newport).¹²⁰⁸ This cell was the first PSC to be certified under a stabilized testing protocol.¹²⁰⁸ The P3HT/graphene composite-based HTL device yielded a champion device with η of 18.2%.¹²⁰⁸ In comparison, the use of sole P3HT as the HTL resulted in a device with inferior performance, *i.e.*, $\eta = 11.1\%$.¹²⁰⁸ The outstanding stability of a unencapsulated device based on P3HT/graphene HTL was demonstrated by only 3% drop after 1680 h storage in ambient conditions with a relative humidity of ~50%.¹²⁰⁸ After encapsulation, the device retained ~89% of its initial η under continuous 1 sun illumination at RT



for 600 h in a N_2 environment.¹²⁰⁸ In comparison, the device using P3HT HTL exhibited rapid degradation, reaching $\sim 25\%$ of its original η after ~ 75 h.¹²⁰⁸ Device stability improvement using GRMs was also demonstrated by Bi and co-workers using a nanostructured carbon layer into the device structure.¹²¹⁰ In particular, an ETL based on PCBM containing N-doped graphene coupled with a carbon quantum dot (CQD) interlayer before Ag CE effectively suppressed the diffusion of ions/molecules within PSCs, preventing perovskite degradation.¹²⁰⁹ In fact, the stable η of a CQDs/G-PCBM-based device over 15% was measured when the device was kept in the dark at RT for 5000 h or under AM 1.5G simulated solar light for 1000 h.¹²⁰⁹ In particular, during the thermal aging test at 85 °C for 500 h, the devices retained 98% of the initial η .¹²⁰⁹

Aurora *et al.* recently reported a breakthrough in the race for the design and realization of stable PSCs.¹⁰³⁸ The authors demonstrated the possible replacement of expensive spiro-OMeTAD with CuSCN as the HTL by achieving a remarkable η above 20%.¹⁰³⁸ The addition of a conductive RGO spacer layer between CuSCN and Au allowed the PSCs to retain more than 95% of the initial η after aging at MPP for 1000 h under 1 sun illumination at 60 °C (Fig. 24).¹⁰³⁸

Graphene was demonstrated to play a major role in reducing the high sheet resistance of PEDOT:PSS used in form of adhesive CEs.¹²¹¹ In fact, PEDOT:PSS was easily spin coated on graphene/PMMA/poly(dimethylsiloxane) (PDMS) substrates to realize the CE, which was subsequently laminated on the

perovskite substrate.¹²¹⁰ When 4-layer graphene was embedded in the CE, a remarkable η value of 12.4% was achieved under light illumination from the FTO side, while device semi-transparency was demonstrated by reporting an η of 4.37% during illumination from the CE side.¹²¹⁰ However, this work was conducted using CVD graphene, and a similar approach based on solution-processed graphene must be consolidated. Notably, the number of graphene layers was key for the device performance optimization.¹²¹⁰ In fact, even though a large number of layers decreases the series resistance, a number of graphene layers higher than 5 compromises the adhesion between graphene and spiro-OMeTAD.¹²¹⁰

An effective approach to improve PSC stability is represented by the replacement of the metal CE with a carbon-based back electrode, to form the so-called carbon perovskite solar cells (C-PSCs).^{1212–1219} In fact, Au is a well-known cause of instability, since it suffers from metal-ion migration phenomenon degrading the perovskite and HTLs when the device experiences an operating temperature above 70 °C.¹²²⁰ So far, three types of C-PSCs have been proposed, namely, mesoporous,¹²²¹ embedment,^{1222–1224} and paintable C-PSCs.^{1125,1126,1225} In mesoporous C-PSCs, a porous carbon electrode is first deposited and then the perovskite is infiltrated within it to complete the structure.^{1218,1220} To produce embedment C-PSCs, a porous carbon electrode is deposited onto a perovskite precursor (*e.g.*, PbI_2), followed by the conversion of the precursor to perovskite by infiltrating a reaction solution.^{1221–1223} Lastly, the carbon CE can be directly deposited onto the

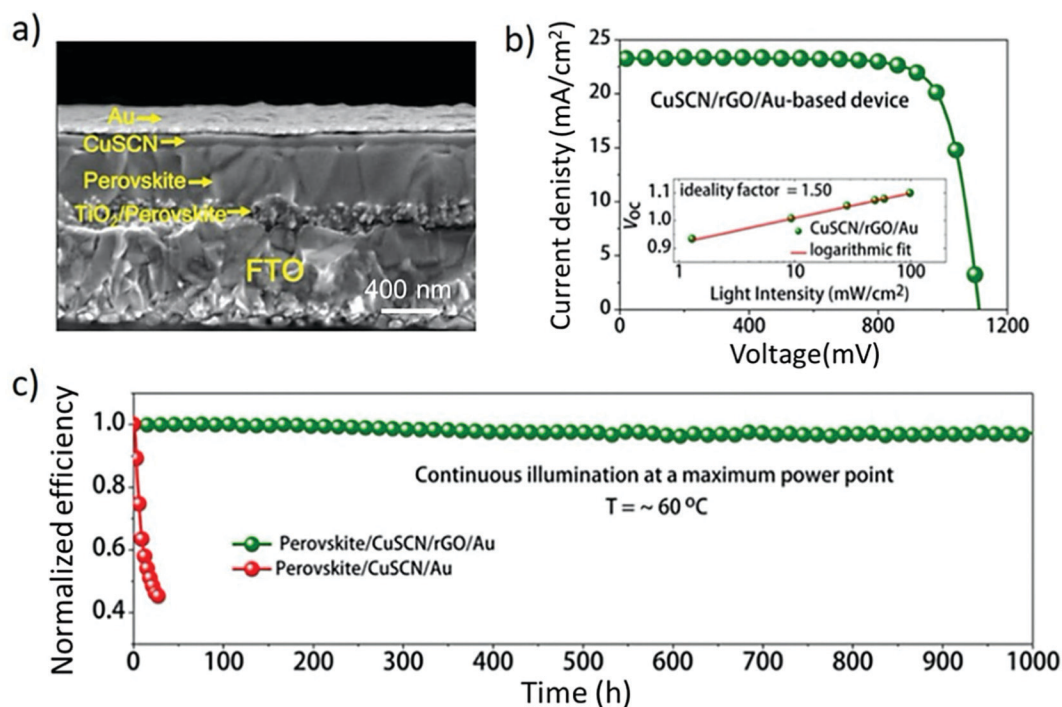


Fig. 24 (a) Cross-sectional SEM micrograph displaying the thickness of different layers in a complete mesoscopic n-i-p PSC employing rGO as the buffer layer between CuSCN-based HTL and Au CE, (b) J - V curve of the CuSCN-based device showing $\eta = 20.4\%$; the inset shows V_{OC} as a function of illumination intensity with an ideality factor of 1.50. (c) Stabilities of an unencapsulated device based on CuSCN HTL and an unencapsulated CuSCN-based device incorporating a thin layer of RGO between the Au and CuSCN layers, evaluated at the MPPs under continuous simulated sunlight illumination at 60 °C in a N_2 atmosphere. Adapted from ref. 1038.



perovskite layer, HTL, or ETL depending on the device configuration (*i.e.*, CTL-free devices, n-i-p, and p-i-n configurations, respectively) to obtain paintable C-PSCs. Recent reviews on C-PSCs summarized the advantages of such technology compared to conventional PSCs,^{1211–1217} including low cost, chemical inertness of the carbon-based material to halide ions, and hydrophobic characteristics. Therefore, we refer the reader to these earlier reviews, while, here, we will specifically focus on the progresses achieved in C-PSCs by using solution-processed 2D materials. In particular, Grancini *et al.* used a 2D/3D (HOOC(CH₂)₄NH₃)₂PbI₄/CH₃NH₃PbI₃ perovskite junction as the active layer to develop 10 × 10 cm² solar modules by a fully printable industrial-scale process, delivering a stable η value of 11.2% for more than 10 000 h with zero loss in performance measured under controlled standard conditions.¹²¹⁸ However, due to poor perovskite layer uniformity, the perovskite infiltration process still represents a critical step, and a facile carbon paste deposition process onto the perovskite is highly pursued. For this purpose, Chen *et al.* recently applied carbon CE over all-inorganic PSCs based on a CsPbBr₃ absorber.¹²²⁷ In this work, Ti₃C₂-MXene nanosheets were used as the interlayer to eliminate energy-level mismatches, accelerate hole extraction, and reduce the recombination at the interface of perovskite/carbon electrode.¹²²⁶ Following this approach, PSCs showing an initial η of 9.0% and long-term stability in a moisture environment over 1900 h (over 600 h under thermal conditions) have been demonstrated.¹²²⁶ As alternatives to conventional carbon paste, SLG, FLG, and multilayer graphene (MLG) have been reported for the realization of metal-free CEs in mesoscopic PSCs.¹²²⁸ In particular, an η value of 11.5% was achieved using reduced multilayered graphene oxide (MGO) at 1000 °C under an Ar atmosphere.¹²²⁷ In comparison to SLG, the better hole extraction of MGO was ascribed to the as-formed Schottky barrier,¹²²⁷ while an ohmic contact was established for the case of SLG.¹²²⁷ Furthermore, larger transport coefficient, longer photocarrier lifetime, and twice the diffusion length have been demonstrated for MGO in comparison with SLG, opening a new route toward the low-cost production of Au-free PSCs.¹²²⁷ N-Doped graphene frameworks (N-GFs), forming covalently bonded 3D structures, were also used as excellent CEs in HTL-free PSCs, achieving an η of 10.32%.¹²²⁹

Recently, Mariani *et al.* reported low-temperature graphene-based carbon pastes in alcoholic solvents compatible with prototypical PSC materials used in standard configurations, namely, the triple cation Cs_{0.05}(FA_{0.85}MA_{0.15})_{0.95}Pb(I_{0.85}Br_{0.15})₃ perovskite and spiro-OMeTAD HTL.¹²³⁰ The corresponding graphene-based CEs have been applied to large-area (1 cm²) mesoscopic devices and low-temperature-processed planar n-i-p devices that reached η values of 13.85% and 14.06%, respectively.¹²²⁹ Moreover, proof-of-concept metallized mini-wafer-like C-PSCs over a substrate area of 6.76 cm² (aperture area = 4.00 cm²) afforded an η of 13.86%, which corresponded to a record-high η value of 12.10% on the aperture area. These results proved, for the first time, the metallization compatibility with such paintable C-PSC configurations.¹²²⁹

Carbon back electrode mechanically stacked with another carbon-coated FTO glass under pressure was also proposed to

realize an innovative modular flexible C-PSC design.¹²³¹ Among the different carbon nanomaterials (*i.e.*, carbon black, graphite sheet, and RGO), RGO has shown η as high as 18.65%, which was the record-high value reported for C-PSCs.¹²³⁰ Furthermore, graphene-based C-PSCs retained 90% of their initial η after aging at an elevated temperature of 85 °C for 1000 h without any encapsulation.¹²³⁰ Very recently, Ti₃C₂ MXenes have been used as the back electrode for mesoscopic n-i-p PSCs in HTL-free configurations. In particular, Ti₃C₂ has been directly deposited over a MAPbI₃ perovskite layer by doctor-blade coating¹²³² or alternatively by using a simple hot-pressing method.¹²³³ Despite the highest η value for PSCs using MXene-based back electrode was 13.83%, the as-produced devices have shown improved stability in the ambient atmosphere at RT (humidity: 30%) compared to gold-based PSCs.¹²³² Table 12 summarizes the main results achieved by PSCs using HTLs and back electrodes based on GRMs.

6.4 Front electrodes (ITO replacement)

GRMs have been recently explored in PSCs with the aim to replace TCOs (*e.g.*, ITO and FTO) used for the TCE in PSC architecture. In fact, ITO and FTO are difficult to fabricate *via* low-temperature solution processes and exhibit poor mechanical flexibility, hindering the development of solution-processed flexible PSCs.^{1235–1237} PEDOT:PSS has also been tested as alternative transparent electrodes.¹²³⁸ However, as a consequence of its hygroscopicity, it can absorb moisture, which decomposes the perovskite layers and rapidly degrades the device performance.¹²³⁹ In this context, graphene and graphene-based nanocomposites have been demonstrated to be reliable alternatives for TCO replacement in both rigid and flexible PSCs. The highest ever reported η (17.1%) on TCO-free rigid devices was claimed in 2016 by Sung and co-workers using CVD graphene substrates.¹²⁴⁰ The tested inverted planar structure reported a graphene/MoO₃/PEDOT:PSS photo-electrode, in which a 2 nm-thick MoO₃ layer improved the PEDOT:PSS deposition onto the hydrophobic graphene surface.¹²³⁹ The lower conductivity of the graphene electrode compared to that of ITO was compensated by the higher transparency and lower surface roughness, resulting in comparable J_{SC} , higher V_{OC} , and improvement of η from 16.9% in ITO/MoO₃-based device up to 17.1%.¹²³⁹ In 2019, Yao and co-workers proposed the use of solution-processed graphene:ethyl cellulose (G:EC) as a transparent electrode for both rigid and flexible substrates using a planar inverted PSC architecture.¹²⁴¹ Apart from the remarkable results achieved on rigid substrates (η = 16.93%), the highly dispersed graphene composite-based transparent electrode satisfied the requirements in terms of σ and T_r for flexible PSCs, resulting in a champion device with an η value of 15.71%.¹²⁴⁰

A different way to replace the TCO layer can be the deposition of Ag conductive grids on rigid or flexible transparent substrates.¹²⁴² However, during initial attempts, the reaction between Ag and halide ions in the perovskite caused rapid, permanent device degradation.¹²⁴¹ To overcome such a limitation, Lu and co-workers proposed a protective GO coating for the Ag grids, and remarkable η of 9.23% and 7.92% were reported for rigid and flexible substrates, respectively.¹²⁴¹ The optimal Φ_w alignment and



Table 12 Summary of the PV performance of PSCs using HTLs or back electrodes based on GRMs^{a,b}

Material	Usage	Device structure	Cell performance			
			J_{sc} [mA cm ⁻²]	V_{oc} [V]	FF	η [%]
(a) GO or (b) WS ₂ or (c) MoS ₂	HTL	ITO/GO or WS ₂ or MoS ₂ /MAPbI _{3-x} Cl _x /PCBM/BCO/LiF/Al	(a) 14.51 (b) 15.91 (c) 14.89	(a) 0.92 (b) 0.82 (c) 0.96	(a) 0.72 (b) 0.64 (c) 0.67	(a) 9.62 (b) 8.02 (c) 9.53
RGD	Dopant for HTL	ITO/GO-PEDOT:PSS/MAPbI ₃ /PC ₆₁ BM/Al	17.1	0.95	0.64	10.6
GO	Dopant for HTL	ITO/PEDOT:PSS:GO-glucose/MAPbI ₃ /PC ₆₁ BM/LiF/Al	17.6	1.05	0.69	12.8
AgOTf-doped GO	Dopant for HTL	ITO/PEDOT:PSS:AgOTf-doped GO/MAPbI _{3-x} Cl _x /PCBM/Au	19.18	0.88	0.7	11.9
GO	Interlayer at front electrode/HTL interface	ITO/GO/PEDOT:PSS/MAPbI ₃ /PC ₆₁ BM/Al	17.96	0.96	0.76	13.1
GO	HTL	ITO/GO/MAPbI _{3-x} Cl _x /PC ₆₁ BM/ZnO/Al	15.59	0.99	0.72	11.11
NGONRs	HTL	FTO/NGONR/MAPbI ₃ /ZnO NPs/Al	17.93	1.00	0.72	12.94
Ammonia modified GO (GO:NH ₃)	Interlayer at HTL/perovskite interface	ITO/PEDOT:PSS:GO:NH ₃ /MAPbI _{3-x} Cl _x /PC ₆₁ BM/Bphen/Ag	22.06	1.03	0.71	16.11
Organosulfate-G (oxo-G)	HTL	Oxo-G1/MAPbI ₃ /PC ₆₁ BM/Zn/Al	18.06	1.08	0.78	15.2
GO	Interlayer at HTL/perovskite interface	FTO/cTiO ₂ /mTiO ₂ /MAPbI ₃ /GO/spiro-OMeTAD/Au	20.2	1.04	0.73	15.1
Iodine reduced GO	Dopant for HTL	FTO/cTiO ₂ /mTiO ₂ /MAPbI ₃ /GO/spiro-OMeTAD/Au	19.6	1.00	0.68	13.33
MoS ₂	Interlayer at HTL/perovskite interface	FTO/c TiO ₂ /mTiO ₂ /MAPbI ₃ /MoS ₂ /spiro-OMeTAD/Au	21.5	0.93	0.67	13.3
(p-Methoxyphenyl -single walled carbon nanotube) SWCNT-PhOMe	Interlayer at HTL/perovskite interface	FTO/c TiO ₂ /mTiO ₂ /MAPbI ₃ /NGO/spiro-OMeTAD/Au	23.6	0.94	0.66	14.6
and RGO	Dopant for HTL	FTO/cTiO ₂ /mTiO ₂ /MAPbI ₃ /P3HT:SWCNT-PhOMe:RGO/Au	18.8	0.87	0.62	10.0
(a) (SLG) or (b) MLG	HTL and back electrode	(a) FTO/cTiO ₂ /mTiO ₂ /MAPbI ₃ /SLG (b) FTO/cTiO ₂ /mTiO ₂ /MAPbI ₃ /MLG	(a) 14.2 (b) 16.7	(a) 0.88 (b) 0.94	(a) 0.54 (b) 0.73	(a) 6.7 (b) 11.5
RGD	Interlayer at HTL/back electrode interface	FTO/TiO ₂ /CsFAMAPbI _{3-x} Br _x /CuSCN/RGO/Au	23.24	1.112	0.782	20.4
MoS ₂	Interlayer at HTL/perovskite	ITO/PTAA/MoS ₂ /MAPbI _{3-x} Cl _x /PCBM/PFN/Al	20.71	1.011	0.784	16.89
Black phosphorus (BP) nanosheets	HTL	FTO/TiO ₂ /MAPbI ₃ /spiro-OMeTAD:BP nanosheets/Au	20.22	1.06	0.761	16.4
Black phosphorous QDs (BPQDs)	Interlayer at HTL/perovskite	ITO/(PEDOT:PSS:BPQDs)/MAPbI ₃ /ZrAcAc-modified PCBM/Ag	20.56	1.01	80.0	16.69
Ti ₃ C ₂ MXenes	Interlayer at perovskite/CE interface	FTO/TiO ₂ /CsPbBr ₂ /MXenes/Carbon	8.54	1.44	0.73	9.01
Graphene	HTL	FTO/TiO ₂ /FAMAPbI ₃ /(PEDOT:graphene)/Au	21.32	0.79	0.518	8.79
Phenyl acetylene silver	HTL	FTO/TiO ₂ /FAPbI ₃ /MoS ₂ /(MAPbBr ₃) _{0.15} /(PTh:graphene)/Au	20.07	0.57	0.43	4.95
(PAS)-functionalized MoS ₂	Dopant for HTL	FTO/(PEDOT:PSS:MoS ₂)/MAPbI ₃ /PCBM/Ag	24.035	0.998	0.686	16.47
RGD functionalized with 4-fluorophenyl-hydrazine	Interlayer at HTL/perovskite interface	ITO/TiO ₂ /MAPbI ₃ Cl _{3-x} /RGO-4FPH/spiro-OMeTAD/Au	21.5	1.11	0.786	18.75
hydrochloride (4FPH)	Interlayer at HTL/perovskite interface	ITO/TiO ₂ /MAPbI ₃ Cl _{3-x} /RGO-4FPH/spiro-OMeTAD/Au	21.5	1.11	0.786	18.75
GO	Dopant for HTL	ITO/GO-doped PEDOT:PSS/(FAPbI ₃) _{0.85} /(MAPbBr ₃) _{0.15} /PC ₆₁ BM/BCP/Ag	20.01	0.90	0.79	14.20
GO	Interlayer at HTL/perovskite interface	FTO/TiO ₂ /MAPbI ₃ /GO/CuBuPC/Au	20.9	1.04	0.66	14.4
GO	Interlayer at HTL/perovskite interface	ITO/PEDOT:PSS/GO/MAPbI ₃ /PCBM/Ag	21.92	0.94	0.748	15.34
MoS ₂	HTL	ITO/MoS ₂ /MAPbI ₃ /PCBM/Al	12.60	0.84	0.57	6.01
RGD	Dopant for HTL	ITO/GO-PEDOT:PSS/MAPbI ₃ /PCBM/BCP/Ag	16.75	0.87	0.75	10.7
MoS ₂	HTL	ITO/MoS ₂ /MAPbI ₃ /C ₆₀ /BCP/Al	20.94	0.88	0.779	14.35
WS ₂	HTL	ITO/WS ₂ /MAPbI ₃ /C ₆₀ /BCP/Al	21.22	0.97	0.73	15.00
GO	HTL	ITO/GO/MAPbI ₃ /C ₆₀ /BCP/Au	21.6	1.00	0.762	16.5
N-Doped graphene frameworks (N-GFs)	HTL and back electrode	FTO/TiO ₂ /MAPbI ₃ /N-GF	20.02	0.87	0.593	10.32
GO	Interlayer at HTL/perovskite interface	ITO/PEDOT:PSS/GO/MAPbI ₃ /PCBM/MoS ₂ /Ag	22.834	1.135	0.738	19.14
GO	HTL and additive for perovskite	ITO/GO/MAPbI ₃ /GO/PCBM/Ag	20.71	0.96	0.76	15.2
Carbon quantum dots (CQDs)	Interlayer at HTL/back electrode interface	FTO/NiMgLiO/MAPbI ₃ /NG:PCBM/CQDs/Ag	19.68	1.07	0.75	15.57
MoS ₂ flakes suspended in 2-propanol (LPE)	Interlayer at HTM/perovskite interface	glass/ITO/PTAA/MoS ₂ /perovskite/PCBM/BCP/Ag	1.13	22.66	0.80	20.55
Antimonene	Interlayer at HTM/perovskite interface	ITO/PTAA/antimonene/CH ₃ NH ₃ PbI ₃ /PCBM/Bphen/Al	1.114	23.52	0.768	20.11
Graphene	Dopant for HTL	FTO/SnO ₂ /TiO ₂ /perov/P3HT-graphene/Carbon	1.09	22.5	0.74	18.2
MoS ₂ QDs:FRGO	Interlayer at HTM/perovskite interface	FTO/TiO ₂ /MAPbI ₃ /MoS ₂ QDs:FRGO/spiro-OMeTAD/Au	1.11	22.81	0.79	20.12



Table 12 (continued)

Material	Usage	Device structure	Cell performance				Ref.
			J_{sc} [mA cm ⁻²]	V_{oc} [V]	FF	η [%]	
fMoS ₂	Interlayer at HTM/perovskite interface	FTO/TiO ₂ /Cs _x (MA _{0.17} FA _{0.83})(1-x)Pb(I _{0.83} Br _{0.17}) ₃ /fMoS ₂ /spiro-OMeTAD/Au	1.14	22.76	0.74	19.2	720
Graphene	Back electrode	FTO/SnO ₂ /Cs _{0.05} MA _{0.16} FA _{0.79} Pb(I _{0.84} Br _{0.16}) ₃ /spiro-OMeTAD/graphene/ITO	1.05	22.78	0.75	18.65	1230
WS ₂ flakes	Interlayer at HTL/perovskite interface	(ITO)/PTAA/WS ₂ /Cs _{0.05} MA _{0.05} FA _{0.95} PbI ₃ /PCBM/BCP/Ag	1.15	22.75	0.81	21.1	1162
Ti ₃ C ₂ MXenes	Back electrode	FTO/cTiO ₂ /mTiO ₂ /MAPbI ₃ /Ti ₃ C ₂	0.89	13.78	0.64	7.78	1231
Ti ₃ C ₂ MXenes	Back electrode	FTO/cTiO ₂ /mTiO ₂ /MAPbI ₃ /Ti ₃ C ₂	0.95	22.97	0.63	13.83	1232
2D black phosphorene (BP)	ETL/perovskite and HTL/perovskite interlayers	FTO/cTiO ₂ /mTiO ₂ /BP/Cs _{0.05} MA _{0.16} FA _{0.79} Pb(I _{0.83} Br _{0.17}) ₃ /BP/spiro-OMeTAD/Au	1.12	23.86	0.74	19.83	1188
Graphene	Back electrode And ETL dopant	FTO/cTiO ₂ /graphene/mTiO ₂ /graphene/Cs _{0.05} (FA _{0.83} MA _{0.15}) _{0.95} Pb(I _{0.85} Br _{0.15}) ₃	1.04	21.8	0.70	15.81	1229
GO	Interlayer at HTL/perovskite interface	FTO/cTiO ₂ /mTiO ₂ /CsPbI ₃ /0.05(FAPbI ₃) _{0.95} (MAPbBr ₃) _{0.05} /spiro-OMeTAD/Au	1.085	22.72	0.75	18.45	1199
BPQDs	Interlayer at HTL/perovskite interface	FTO/cTiO ₂ /mTiO ₂ /CsPbI ₃ /0.05(FAPbI ₃) _{0.95} (MAPbBr ₃) _{0.05} /spiro-OMeTAD/Au	1.085	23.12	0.75	18.86	1199
MoS ₂	Interlayer at HTL/perovskite interface	FTO/cTiO ₂ /mTiO ₂ /CsPbI ₃ /0.05(FAPbI ₃) _{0.95} (MAPbBr ₃) _{0.05} /spiro-OMeTAD/Au	1.095	23.05	0.75	19.03	1199
BP nanosheets	Interlayer at HTL/perovskite interface	FTO/cTiO ₂ /mTiO ₂ /CsPbI ₃ /0.05(FAPbI ₃) _{0.95} (MAPbBr ₃) _{0.05} /spiro-OMeTAD/Au	1.11	23.40	0.78	20.32	1199
2DP-TDB	HTL	ITO/SnO ₂ /FA _{0.85} MA _{0.15} PbI ₃ + 4-fluorobenzamide hydrochloride (p-FPhFACl)/2DP-TDP/MoO ₃ /Ag	1.16	24.02	0.796	22.17	1207

^a MA = CH₃NH₃, ^b FA = HC(NH₂)₂.

surface wetting of Ag nanonetwork compared to PEDOT:PSS HTL were finely controlled *via* the reduction degree of GO flakes by means of a self-assembly approach at room temperature.¹²⁴¹

It is worth noting that the feasible realization of solution-processed conductive front electrode opens the route toward large-scale, low-cost fabrication of PSCs exclusively through R2R technologies.

Table 13 summarizes the main results achieved by PSCs using graphene-based front electrodes. Some representative results achieved using nonsolution-processed graphene (*i.e.*, CVD graphene) are also reported to facilitate comparison.

6.5 Two-dimensional/three-dimensional PSCs

As discussed in the introduction of Section 6, careful interface engineering between the perovskite active layer and CTL (ETL/HTL) is pivotal to push device development and optimization. Beyond interface engineering with graphene and other GRMs, the use of a layered perovskite, namely, 2D perovskites, has recently attracted a lot of interest.^{1243,1244} This is motivated by their superior stability against moisture, far exceeding those of their standard 3D parent structures.^{111,1242} Layered perovskites usually possess the general structure R₂A_{*n*-1}B_{*n*}X_{3*n*+1}, where A, B, and X are the organic cation, metal cation, and halide anion typically forming the 3D perovskites, while R is a large organic cation (for example, aliphatic or aromatic alkylammonium), functioning as a spacer between the inorganic layers. In the structure, *n* determines the number of inorganic sheets held together (Fig. 25a). By controlling the A/R ratio, the *n* value could be adjusted from *n* = 1 (2D), *n* > 1 (quasi-2D), and *n* = ∞ (3D).^{111,1016,1040–1042,1245} For low *n*, 2D perovskites have large *E_g* and stable excitons with large binding energy and limited transport through the organic spacer.^{110,111} Such properties limit the PV effect, leading to poor performances in SCs.^{111,1246} By increasing *n*, the device η improves (Fig. 25b) in concomitance with a decrease in bandgap and improvement in charge transport across the inorganic layers, reaching values up to 17%.¹¹¹ A large family of R cations can be inserted forming a layered 2D material, as shown in Fig. 25c. This family includes, for example, an organic cation designed *ad hoc* with additional functional groups or atom (such as fluorine moieties) to enhance the water repellent characteristics of the material.^{1247,1248} Importantly, compared to 3D perovskites, 2D perovskites show remarkably higher moisture resistance, due to the hydrophobic nature of the R cation, as well as the highly oriented crystalline structure and dense packing.^{1246,1247} These properties reduce the possibility of direct contact of water or oxygen molecules within the perovskite grain boundaries.^{1246,1247}

The integration of 2D perovskites into PSCs as a stabilizer component has become increasingly popular in the last few years as a tool to increase the lifetimes of PSCs. Beyond that, a 2D perovskite also functions as a surface passivation layer, significantly improving the device V_{oc} .^{1249,1250} In detail, the most common approach intends to combine the high efficiency of 3D perovskites with the superior stability of 2D perovskites by means of synergistic interface functionalization. This has been demonstrated by either mixing the 2D and 3D precursors together^{110,111} or by engineering a layer-by-layer deposition



Table 13 Summary of the PV performance of PSCs using graphene-based front electrodes^{ab}

Material	Usage	Device structure	Cell performance				Ref.
			J_{sc}	V_{oc}	FF	η	
CVD graphene (CVD-G) (not solution-processed)	Transparent back electrode	FTO/cTiO ₂ /MAPbI _{3-x} Cl _x /spiro/PEDOT:PSS:sorbitol/PDMS-PMMA-CVD-G	19.17	0.96	0.67	12.37	1210
CVD-graphene (CVD-G) (not solution-processed)	Front electrode	CVD-G/molybdenum trioxide (MoO ₃)/PEDOT:PSS/MAPbI ₃ /C ₆₀ /BCP/LiF/Al	21.9	1.03	0.72	17.1	1239
Single-layer graphene (SLG) (not solution-processed)	Bottom contact for top cell in tandem configuration	Bottom cell: crystalline silicon top cell: SLG/PEDOT:PSS/spiro-OMeTAD/MAPbI _{3-x} Cl _x /TiO ₂ /FTO/glass	21.9 (Top cel from FTO side)	0.96 (Top cel from FTO side)	0.56 (Top cel from FTO side)	11.8 (Top cel from FTO side)	1272
Nano-composite of silver nano-network and GO	Front electrode	Substrate/Ag nanonetwork/GO/PEDOT:PSS/MAPbI ₃ /PCBM/PFN-P1/Ag	13.78	0.94	0.71	9.23	1241
Graphene:ethyl cellulose (G:EC)	Front electrode	Substrate/G:EC transparent electrode/perovskite/PCBM/Ag	1.06	20.68	0.77	16.93	1240

^a MA = CH₃NH₃. ^b FA = [HC(NH₂)₂].

method to obtain a clean 2D/3D vertical bilayer architecture.^{966,1041,1042,1251,1252} The top 2D perovskite layers can simultaneously act as surface passivators, improving the surface robustness and hydrophobic character of the active layer, while also reducing surface charge recombination, ultimately improving the device open-circuit voltage.^{1040,1041,1059,1247,1253} Cho *et al.* developed a method for the deposition of a 3D/2D bilayer composed of mixed halide perovskites and (PEAI)₂PbI₄ (PEAI = phenethylammonium iodide).¹²⁵¹ The layer-by-layer growth is induced by the spin coating of PEAi in an isopropanol solution on the mixed halide 3D perovskite with PbI₂ excess.¹²⁵¹ The PbI₂ excess has been demonstrated to segregate on top of the 3D perovskite, reacting *in situ* with PEAi at the top surface and forming a thin 2D layer on top of the 3D material (the model of the device architecture is shown in Fig. 25d and e).

Since the 2D perovskite lies on the top surface at the interface with the HTM, the interfacial charge carrier recombination is reduced, increasing η to values higher than 20%.¹²⁵¹ More recently, Jung *et al.* reported a double-layered halide architecture incorporating an ultrathin wide-bandgap halide stacked onto a narrow-bandgap halide light-absorbing layer. This layer effectively reduced charge recombinations at the perovskite/P3HT interface, resulting in an η value of around 23% and long-term operational stability.⁹⁶⁶ In addition to improving the surface robustness, imparting hydrophobicity, and passivating the surface, it has been recently demonstrated that the 2D overlayer is also crucial in preventing ion diffusion at the interface with the HTM.^{1040,1041} Sutanto *et al.* indeed observed a slower evolution (timescale of months) of the PV characteristics of 2D/3D PSCs using thiophene alkylammonium-based

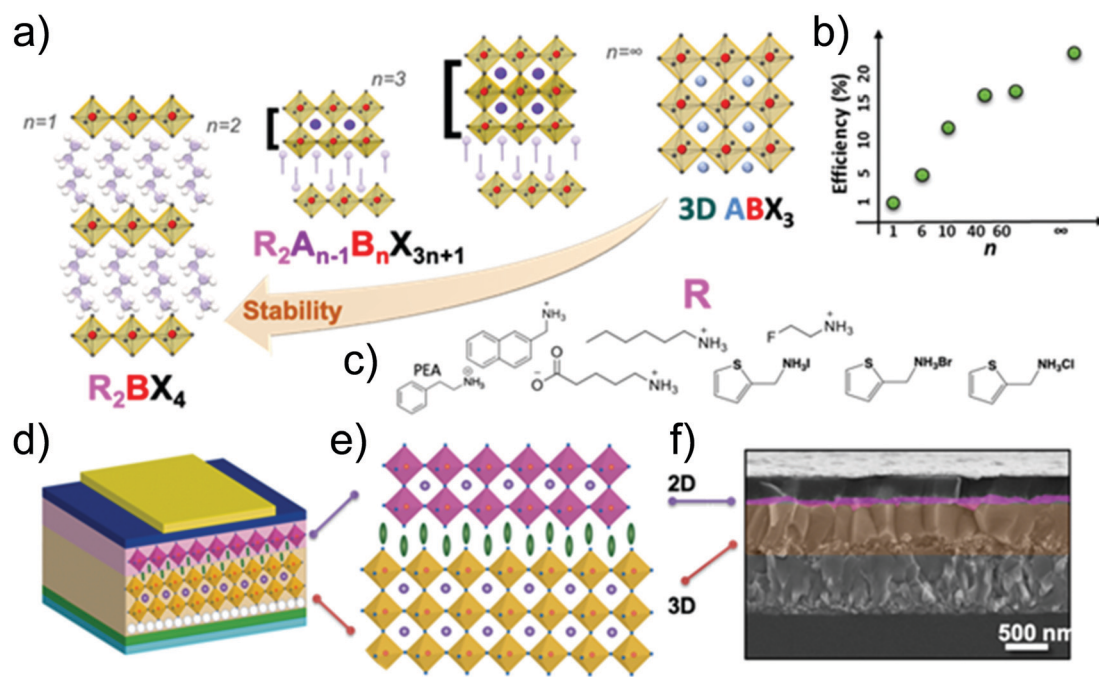


Fig. 25 (a) Structure of perovskite from 2D to 3D forms. (b) η versus n . (c) Typical cations used as R for the 2D perovskite formulation. (d) Structure of an n-i-p PSC based on FTO; cTiO₂, mTiO₂, 3D/2D perovskite, organic HTM, and Au CE. (e) Schematic of the 3D/2D active perovskite layer. (f) Cross-sectional SEM image of the 2D/3D device.



organic cations as the building blocks for the 2D perovskite (Fig. 25c).^{1040,1041} A boost in η has been associated with the slow structural rearrangement of the 2D/3D interface, which depends on the “softness” of the 2D perovskite overlayer that can act as an ion scavenger.¹⁰⁴⁰ Because of the movement of ions in the 3D perovskite, small MA cations accumulate at the interface.¹⁰⁴⁰ The 2D structure can incorporate the MA cations by altering its pristine layered structure into a mixed (or quasi-2D) phase.¹⁰⁴⁰ In addition, a “more robust” 2D layer can prevent such structural changes, mechanically blocking the movement of ions.¹⁰⁴⁰ This ion blockage leads to a dramatic increase in device stability, while maintaining high device η .¹⁰⁴⁰ In addition, these 2D modifiers also dramatically improve the thermal stability of PSCs,¹⁰⁴⁰ demonstrating that a conscious choice of proper 2D components can control the structural, physical, and energetic properties of the 2D/3D interfaces, a key element to be controlled for the design and realization of efficient and stable devices.¹¹ While defining the interface structure–function relationship is of utmost importance to control ion and charge accumulation and dynamical effects, the exact knowledge on interface energetics is also pivotal. To this end, it has been recently demonstrated that such thiophene-based cations form a p–n junction at the 2D/3D interface, which is the key to enable efficient charge transfer. As a consequence, electron accumulation at the interface is reduced, nullifying interfacial recombinations. This beneficial effect is reflected in the device V_{OC} , which reached 1.19 V, among the highest reported so far in the literature.¹²⁵⁴ As an illustrative example, an intact 2D/3D heterojunction, realized by growing a stable and highly crystalline 2D $(C_4H_9NH_3)_2PbI_4$ film on top of a 3D perovskite (using a solvent-free solid-phase in-plane growth), reached a certified steady-state η of 24.35%, while retaining 94% of its initial η after 1056 h under the damp heat test (85 °C/85% relative humidity) and 98% after 1620 h under 1 sun illumination (without any encapsulation).¹²⁵⁵ Meanwhile, substantial progresses have been recently achieved in controlling the film formation of 2D perovskites.¹²⁵⁶ For example, an η value of 15.81% has been achieved using hot-cast Dion–Jacobson 2D perovskite $((PDMA)(MA)_{n-1}Pb_{n-1}I_{3n+1})$ ($PDMA = 1,4$ -phenylenedimethan ammonium; $\langle n \rangle = 4$) as the photoactive layer.¹²⁵⁵ Moreover, by elucidating the critical role of additives in regulating the nucleation and crystallization kinetics of 2D $(PEA)_2(MA)_3Pb_4I_{13}$ films with low trap states and desired carrier transport/collection properties, Yang *et al.* recently achieved an η value up to 18.5%, together with FF of 83.4%.¹²⁵⁷

6.6 Tandem SCs based on PSCs

The tunability of the E_g value of perovskites *via* halide replacement¹²⁵⁸ or cation exchange¹²⁵⁹ and their high absorption coefficient across the entire visible range¹²⁶⁰ make these materials attractive for tandem SCs, particularly in combination with Si sub-cells.

In a Si/perovskite tandem configuration, higher-energy photons are absorbed by the perovskite sub-cell, while infrared photons are transmitted through the perovskite top cell and

absorbed by the Si sub-cell, covering a wide absorption spectral range defined by the E_g value of Si.^{1261,1262}

Therefore, the perovskite-based tandem configurations require the stacking of constituent sub-cells, with the perovskite top cell having two transparent electrodes, one of them directly processed on top of the charge selective layer (*e.g.*, spiro-OMeTAD).^{1263,1264} Both high σ and optimal T_r of the top-cell transparent electrode are the key requirements for the successful design/realization of tandem devices. Conventional TCOs optically optimized for single-junction devices cannot be easily deposited onto the perovskite top cell due to the ion bombardment-induced degradation of the underlying materials during TCO sputtering.^{1265,1266} A strategy to minimize the underlying material damage is the deposition of additional buffer layers, which can absorb the energy impact of ions crashing on the device. Either thermally evaporated sub-stoichiometric molybdenum oxide (MoO_x) buffer layers^{1267,1268} or ultrathin layers of Au¹²⁶⁹ have been reported to protect spiro-OMeTAD during TCO sputtering. However, the aforementioned strategies inevitably add complexity to the perovskite top-cell fabrication process or cause additional optical losses. Moreover, the simplest solution offered by the MoO_x buffer raises concerns on long-term stability, since the iodide of the perovskite layer can chemically react with MoO_x , resulting in an unfavorable interface energy-level alignment for hole extraction.¹²⁷⁰

In order to address these challenges, transparent graphene-based electrodes are promising for the realization of efficient and stable bifacial PSCs. Although graphene-based electrodes for PSC-based tandem SCs produced by solution-processed methods are still missing, several groups already reported their practical implementation through other techniques, such as CVD. For example, Lang and co-workers addressed this challenge by implementing large-area CVD-graphene as a highly transparent photoelectrode in a perovskite top-cell.¹²⁷¹ In fact, the electrodes based on graphene combined an excellent T_r (97.4%) with R_s of 100 $\Omega \square^{-1}$.¹²⁷² Zhou and co-workers demonstrated two-layer CVD graphene as a transparent contact for a top cell based on a Cl-doped perovskite film with a bandgap of 1.59 eV.¹²⁷³ The graphene electrodes permitted to achieve a top-cell η of 11.8%, resulting in a tandem SC with an η of 18.1%.¹²⁷²

Even though solution-processed 2D material-based recombination layers or transparent conductive contacts have not been demonstrated in tandem devices yet, the use of graphene in the ETL of the perovskite top-cell was recently reported in a two-terminal (2T) mechanically stacked Si/perovskite tandem SCs.¹²⁷⁴ With this approach, the sub-cells were fabricated and independently optimized and subsequently coupled by contacting the back electrode of the mesoscopic perovskite top-cell with the texturized and metallized front contact of the silicon bottom cell.¹²⁷³ Then, the graphene-doped mesoporous ETL used in the perovskite top-cell allowed the tandem SCs to improve their η up to 26.3% over an active area of 1.43 cm^2 .¹²⁷³ Overall, the “mechanical approach,” based on the independent optimization and fabrication of sub-cells, as well as graphene-based top cell, is ready to synergistically exploit the most recent progress achieved in both PSCs and Si



cells in order to boost perovskite/silicon tandem SCs beyond current PV technology established in the market.¹²⁷³

6.7 Summary and outlook

PSCs are an exciting PV technology aiming to enter a massive market. In fact, they can be produced through scalable and cost-effective solution-based techniques compatible with R2R and S2S manufacturing processes,¹²⁷⁵ while reaching outstanding η up to certified values of 25.2%.⁸⁹⁷ This value approach to the record-high η of monocrystalline and HIT Si SCs (26.1 and 26.7%, respectively),⁸⁹⁷ even superior to those of thin-film PV technologies, such as CdTe and copper indium gallium selenide (CIGS) SCs (22.1% and 23.4%, respectively).⁸⁹⁷ Furthermore, perovskite-based tandem SCs, namely, perovskite-Si tandem SCs, have reached certified η up to 29.1%,⁸⁹⁷ which is as high as the value of costly GaAs SCs (that holds the record-high certified η for single-junction cells).⁸⁹⁷ Prospectively, the LCOE of perovskite solar panels has been estimated to be lower than 5 US cents kW h⁻¹.^{131–133} This value is competitive with the LCOEs of fossil fuels,^{134,135} thus enabling the achievement of grid parity. However, the instability of photoactive perovskites^{1001,1276–1278} and CTLs^{1001,1277} represents the main technical barrier for PSC technology. In this scenario, the use of solution-processed 2D materials in PSCs demonstrated exciting results in resolving current PSC issues, boosting both stability and η by means of scalable and cost-effective strategies.^{1037,1279,1280} These advances can be ascribed to the progresses achieved in the preparation of 2D material inks and their large-area (*i.e.*, wafer-scale) printing,^{205,297,1281,1282} addressing controllable optoelectronic properties to be exploited in PSC structures.¹¹⁹² By formulating 2D material-based inks in solvents compatible with materials composing the PSCs, GRMs have been successfully integrated as both CTLs and interlayers,¹²⁸³ improving the charge collection (while providing effective barriers against humidity) and migration of ions within the PSC structures.^{1037,1284,1285} Graphene and its derivatives have also been investigated to form efficient back electrodes (CE) as an alternative to Au or Ag.^{1217,1227} Beside reaching relevant η up to 18.65%,¹²³⁰ the use of metal-free back electrodes eliminates the degrading reaction between the perovskite layer and Au and Ag, which are the cause of device instability.^{1219,1286,1287} Recent advances in low-temperature processable graphene inks are promising for the realization of paintable C-PSCs based on structures that achieved record-high η using metal-based back electrodes.¹²¹⁷ Importantly, graphene and other GRMs (*e.g.*, MoS₂) can also regulate the perovskite crystal over both mesoscopic scaffolds and planar CTLs,^{1104,1160} increasing the reproducibility of high- η devices. Besides, pristine FLG flakes were used to stabilize perovskite films, slowing down charge thermalization.¹¹⁰⁶ The realization of 2D material-enabled hot-carrier extraction and collection paves the way for the creation of advanced SC concepts, which are still unexplored.¹¹⁰⁶

Despite the implementation of GRMs has not been reported yet for PSCs showing state-of-the-art η , outstanding results have been achieved in large-area PSCs and PSMs.¹¹⁹² The deposition of 2D material-based inks by means of printing techniques, such as slot-dye coating, blade coating, spray coating, and

screen printing have been established in a wide range of applications, including energy storage and conversion systems beyond SCs.^{5,207,1288} For the case of PSCs, the printing processes of 2D materials can be easily customized and optimized in combination with a protective layer on top of the perovskite absorber, such as 2D perovskite¹²⁸⁹ or polymeric interlayer (*e.g.*, PMMA).¹²⁹⁰ As a striking example of PSC scale-up, some authors of the present review (belonging to University of Rome Tor Vergata, Hellenic Mediterranean University, Italian Institute of Technology, and BeDimensional S.p.A.), in collaboration with the industrial partner GreatCell Solar, realized the first example of real-time characterized, standalone 2D-material-enabled perovskite solar farm. The latter was installed in Heraklion (Crete), a site with favorable climate conditions. Initially, it comprised 9 solar panels, each one with an active area of 0.32 m² (Fig. 26). According to the planned activity, other panels will be integrated into the solar farm, and the output of the solar farm will be continuously monitored, providing a clear understanding of (1) the correlation of environmental conditions with the outdoor performance of solar panels and (2) the benchmarking of 2D material-based perovskite solar panels against conventional PV technologies (Si, CdTe, and CIGS). The preliminary data, provided to the Commission of the European Union (project founders),¹²⁹¹ revealed the key advantages of 2D materials in providing PV FoMs competitive in the market, bringing PSC commercialization closer to reality. It is noteworthy that under the umbrella of European Graphene Flagship, the solar farm project has been recently extended to a graphene-integrated perovskite-silicon tandem SC technology, involving a key player of the PV industry, namely, Enel Green Power and Siemens.^{1292,1293} Not by chance, the results achieved using 2D materials on single-junction PSCs have already been exploited in perovskite-based tandem SCs, namely, a perovskite-Si tandem device.¹²⁷³ In particular, the doping of TiO₂-based ETLs of PSCs with graphene flakes enabled the tandem devices to reach η over 26%.¹²⁷³ Nevertheless, the incorporation of GRMs in perovskite-based tandem devices is still at a premature stage. Prospectively, solution-processed graphene and other metallic 2D materials can play a major role in developing advanced interconnecting layers with a satisfactory trade-off between optical transparency and electrical conductivity.



Fig. 26 2D materials-enabled perovskite solar farm installed in Heraklion (Crete).



Lastly, it is worth noting that 2D materials can play a relevant role in developing new encapsulation strategy for perovskite devices, which are particularly sensitive to oxygen, moisture, and volatilization of internal species (*i.e.*, decomposition products and dopants).^{1294,1295} For example, a recent work demonstrated a cost-effective and scalable flexible transparent lamination encapsulation method based on graphene films with a PDMS buffer on a PET substrate.¹²⁹⁶ Moreover, the impermeability of graphene or other related materials can be successfully exploited to create novel encapsulants or edge sealers, decreasing the water vapor transmission rate (WVTR) or oxygen transmission rate (OTR) of the current encapsulants used in PSCs, as well as other PV technologies.

Overall, 2D materials are expected to play protagonists in the optimization of perovskite-based PV technology, which could represent a game changer in the PV market for the near future.

7. Other SCs

7.1 QDSCs

QDSCs are an attractive PV technology owing to various advantages,¹²⁹⁷ such as cost-effectiveness and simple device manufacturing processes.^{57,1298–1307} As comprehensively discussed in recent review articles (for example, ref. 1296), such SCs are based on photoactive semiconductors (organic, inorganic, or hybrid) QD films, which act as both absorbers and charge transporting media. Different types of QDSC architectures have been proposed: (1) Schottky QDSCs, which consist of a heterojunction between a planar film of p-type colloidal QDs and a shallow- Φ_w metal, which produce a Schottky barrier generating a depletion region for carrier separation;^{1308–1313} (2) depleted heterojunction QDSCs, which use a highly doped n-type metal oxide (typically, TiO_2 or ZnO , but even metal chalcogenides, *e.g.*, CdS) in a p–n heterojunction with a p-type QD film;^{1314–1316} (3) heterojunction QDSCs, also referred to as QD-sensitized solar cells (QDSSCs), in which the n-type wideband-gap semiconductor and QD film form an interpenetrating layer.^{1296,1301,1317–1325} This structure is usually obtained by infiltrating QDs into the structured n-type semiconductors. Since this architecture resembles that of DSSCs, such cells are often referred to as QD-based DSSCs (QDDSSCs) (see Section 5); (4) quantum junction QDSCs, which consist of a homojunction-like architecture where both p- and n-type materials of the junction are composed of QDs;¹³²⁶ (5) bulk nanoheterojunction SCs in which an n-type material and p-type QDs are mixed similar to a BHJ architecture.¹³²⁷

The optoelectronic properties of semiconductor QDs, *e.g.*, E_g , optical absorption coefficient (α), and charge carrier transport, can be effectively tuned by modulating their size and shape,^{1298–1304,1328} offering versatile systems to be used in graded doping architectures^{1329–1331} and multijunction (tandem) SCs.^{1332,1333} Initially, chalcogenide semiconductors, such as CdX and PbX ($X = \text{S}, \text{Se}, \text{and Te}$), have been used for QDSCs due to their ability to harvest light in the visible and IR regions and their low cost.^{1300,1304–1306,1327,1334} However, the limited η achieved with these inorganic QDs drove researchers to design

novel QDs, including inorganic alloys, organic, and organic–inorganic hybrid QDs with superior PV capabilities.^{1304–1306,1327} Therefore, over the past decade, QDSCs have seen rapid improvements, until reaching a certified η value of 16.6% with mixed Cs and formamidinium lead triiodide perovskite system¹³³⁵ (previous record was 13.4%).¹³³⁶ These important results are the fruits of progress achieved in both control of the QD surface chemistry and the understanding of device physics,^{1305,1306,1337} and they are now leading QDSCs toward commercialization.^{1305,1306}

Despite recent progresses, the record-high η of the QDSCs is still far from their theoretical maximum η , which is as high as 33%¹³³⁸ (or 44%, depending on whether or not multiple exciton generation of the QDs is considered).^{1337,1339} Actually, the major issue in QDSCs is the presence of structural defects or unpassivated states on the QD surface, which leads to recombination reactions limiting the overall performance of the devices.^{1340–1347} To resolve this issue, several strategies, including the implementation of atomic ligand/anionic passivation schemes,^{1348–1350} use of passivation layers over QD films,^{1351–1355} and design of core–shell structures,^{1356–1363} have been developed in various type of QDSCs. For example, a hybrid passivation scheme, which introduces halide anions during the end stages of the QD synthesis process, was used to realize depleted heterojunction QDSCs with a certified η value of 7.0%.¹³⁴⁷ Sequential inorganic ZnS/SiO_2 double-layer treatment onto the QD-sensitized photoanode strongly inhibited the interfacial recombination processes in QDSSCs, which reached a certified η value of 8.21%.¹³⁵⁴ CdSeTe/CdS type-I core–shell QDSSCs, obtained by overcoating CdS shells around CdSeTe -core QDs, achieved an η value of 9.48%.¹³⁵⁷ Binary QD films have also been investigated in heterojunction QDSCs in order to improve the charge separation using p–n junctions at the nanoscale, while passivating possible surface defects of QDs.^{1326,1364,1365} In addition, such junctions enabled the dissociation of excitons in free carriers, drastically reducing bimolecular recombination processes.^{1326,1363,1364} The use of mixed QD films was targeted to extend the carrier diffusion length, allowing thicknesses of the photoactive films to become comparable to the optical absorption length.^{1363,1364} However, binary QD systems have limitations in simultaneously controlling the E_g value as well as CB and VB edges for both charge photogeneration and collection. Hence, to overcome the limitations of binary QDs, alloy QDs^{1366,1367} and hybrid organic–inorganic QDs^{1334,1368,1369} have been successfully proposed together with the abovementioned strategy to passivate surface defects. For example, Du *et al.* reported a Zn–Cu–In–Se -alloyed QD sensitizer to construct Pb- and Cd-free QDSSCs with a certified η value of 11.61%.¹³⁷⁰ Very recently, the $\text{Cs}_{1-x}\text{FA}_x\text{PbI}_3$ system in the form of QDs enabled the realization of QDSSCs with a certified record η of 16.6%, together with superior stability (94% of the original η under continuous 1 sun illumination for 600 h) compared with their thin-film counterpart.¹³³⁴

In addition to the aforementioned strategies, the engineering of various QDSC configurations through the introduction of interfacial layers and doping of components is crucial to improve the charge extraction and transport from the photoactive layer to the metal contacts, thereby achieving performance rivaling those



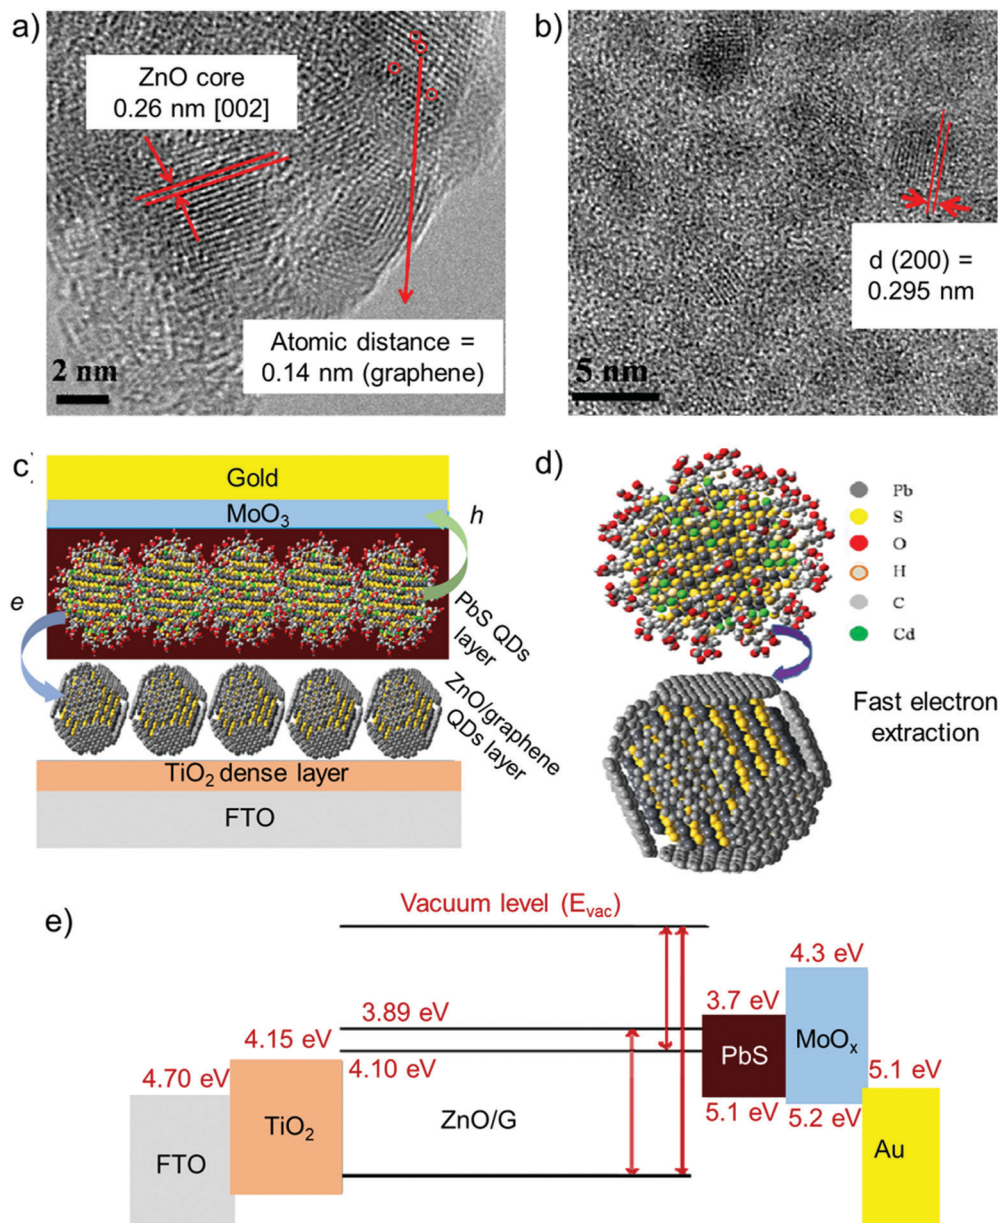


Fig. 27 High-resolution TEM images of (a) graphene QDs and (b) ZnO/graphene QDs. (c) PbS QD and ZnO/graphene QD-based depleted heterojunction QDSCs. (d) Schematic of the electron extraction process from PbS QD to ZnO/graphene QD. (e) Energy-level diagram of PbS QD- and ZnO/graphene QD-based depleted heterojunction QDSCs (G = graphene). Adapted from ref. 1370.

of other PV technologies. Especially in this context, solution-processed graphene and other 2D materials have attracted a primary interest for QDSCs. Tavakoli *et al.* reported an *in situ* solution-based process to prepare hybrid ZnO/graphene QDs (Fig. 27a and b), where the graphene shell quenches the PL intensity of ZnO nanocrystals (size of NPs: 5 nm) by ~72%, primarily due to charge transfer and static quenching.¹³⁷¹ This nanocomposite was used as a CE material in a PbS/TiO₂ depleted heterojunction QDSCs, which achieved an η value of up to 4.5%.¹³⁷⁰ Fig. 27c shows a schematic of the architecture of the device, in which fast electron extraction is achieved by means of ZnO-graphene CE (Fig. 27d).¹³⁷⁰ In particular, the band diagram of device shows the electron extraction process from PbS to ZnO-graphene-coated TiO₂ (Fig. 27e).¹³⁷⁰

The authors explained their results by suggesting efficient electron injection from the CB of ZnO QDs to the LUMO levels of graphene, which occurs through Zn–O–C bonding, and slow electron recombination in the presence of ZnO-graphene buffer layer.¹³⁷⁰ Graphene frameworks were incorporated into the TiO₂ photoanode as an electron transport medium to improve the PV performance of QDSSCs (up to an η value of 4.2%) owing to their excellent conductivity and isotropic framework structure.¹³⁷²

Kim *et al.* reported the use of a hierarchical ZnO nanostructure array, produced by a two-step solution reaction and composed of nanosheet branched ZnO nanorods as an efficient anode for QDSSCs.¹³⁷³ This 2D (nanosheet)–1D (nanorod) combined hierarchical ZnO nanostructure considerably enhanced light



capture compared with ZnO thin films and ZnO nanorods, allowing the corresponding CdSe/CdS-based QDSSCs to achieve an η value of 4.4%.¹³⁷²

Recently, 2D MoS₂ nanosheets were used as an efficient HTL for PbS-based depleted heterojunction QDSCs.¹³⁷⁴ All-solution-processed n-p-p⁺ architecture was fabricated by sequentially depositing ZnO NPs, PbS QDs, and 2D MoS₂ nanosheets acting as n-, p-, and p⁺-type layers, respectively.¹³⁷³ The incorporation of MoS₂ HTL improved the η value from 0.92% (in the free-MoS₂ reference) to 2.48%.¹³⁷³

Noteworthy, 2D MoS₂ has recently been coupled to Sn-doped In₂O₃ nanocrystals to collect holes from the latter and driving permanent charge separation across a novel type of ultrathin solid-state 0D/2D hybrid interface that can store light in the contactless mode.¹³⁷⁵ Therefore, these results further prove the potential of MoS₂ as the HTL in QD-based optical devices.

Jin *et al.* reported graphdiyne, which is a π -conjugated structure consisting of sp²- and sp-hybridized carbons in a typical 2D configuration, as a potential solution-processed hole transporter for PbS-based QDSCs, which reached an η value of 10.64%.¹³⁷⁶ The use of graphdiyne-based anode buffer layer improved hole extraction from the QDs to Au anodes, while providing long-term shelf-life stability over 120 days.¹³⁷⁵

Dangling bond-free 2D h-BN with self-terminated atomic planes, produced through LPE in 2-propanol, was used to passivate the TiO₂ surface in CdSe-based QDSCs.¹³⁷⁷ By decreasing the recombination rate at the TiO₂/CdSe interface, the resulting QDSCs achieved an η value of 7%, corresponding to a 46% improvement in η exhibited by the h-BN-free reference.¹³⁷⁶

In addition to the aforementioned roles of 2D materials in QDSCs, liquid-phase synthesized antimonene QDs have been applied as the photoactive layer in QDSSCs.¹³⁷⁸ Owing to their strong light-matter interaction, moderate E_g for an optimal absorption in the visible spectrum, and antioxidation properties, antimonene QDs enabled the realization of QDSSCs with an η value up to 3.07%.¹³⁷⁷ Moreover, the as-fabricated SCs have shown long-term stability, retaining more than 90% of the initial η after 1000 h.¹³⁷⁷ Therefore, antimonene QDs, as well as other 2D material-derived QDs, may provide a new pathway for a novel kind of cost-effective solution-processed QDSCs.¹³⁷⁷

Although the above examples clearly indicate that 2D materials can play a significant role in further improving the performance of QDSCs, their use in this type of SCs is not strongly established as those for OSCs, DSSCs, and PSCs. However, both the advent of a novel type of efficient QDSCs and successful implementation of 2D materials in other PV devices can provide the fundamentals for the future establishment of 2D material-enabled efficient QDSCs.

7.2 Organic-inorganic hybrid SCs

Organic-inorganic hybrid SCs combine organic and inorganic materials as the photoactive material. As discussed in previous reviews in the literature,^{1379–1385} the rationale of this combination is to implement the advantages offered by both OSCs and inorganic components. As proposed for OSCs (Section 3), organic materials are solution-processable and thus compatible with low-cost and high-throughput deposition methods, including R2R

printing techniques. Moreover, they have high σ in the visible spectrum. Thus, they allow their thin (thickness of a few hundred nanometers) films to efficiently absorb solar light. Meanwhile, inorganic materials can be formulated in the form of solution-processable nanocrystals with tunable optoelectronic properties, as shown in Section 7.1 for QDSCs. Furthermore, they have a large dielectric constant (*e.g.*, ~ 10.4 for CdSe),¹³⁸⁶ which decreases the Coulombic attraction between electrons and holes, facilitating their separation in free charges. Thus, when mixed with organic photoactive components, they can provide an interfacial force driving the dissociation of excitons generated in the organic materials in free charge.^{1387–1390} Therefore, inorganic nanocrystals can act as ideal acceptor materials in BHJ OSC-like devices using either organic polymers or conjugated small molecules as the donors.^{1378–1384,1391}

The first hybrid SC was reported in 1996 using CdSe nanodots as the acceptor and poly[2-methoxy-5-(2'-ethylhexyloxy)-p-phenylene vinylene] (MEH-PPV) as the donor.¹³⁹² However, the corresponding η was low ($< 0.5\%$) as a consequence of the poor charge transport through the CdSe nanodots.¹³⁹¹ Thereafter, much effort has been devoted toward improving charge transport by tuning the nanocrystal shapes.^{1393–1395} Studies on QDSCs also helped to rapidly advance hybrid SCs.¹³⁹⁶ In 2011, Ren *et al.* reached an η value of 4.1% with hybrid SCs based on P3HT and CdS nanocrystals as the donor and acceptor, respectively.¹³⁹⁷ More recently, hybrid SCs based on Si as the inorganic component have drawn relevant attention due to their room-temperature, facile, and cost-effective fabrication processes, which is promising to lower the cost of conventional Si SCs.^{1398–1400} Owing to advances in the synthesis of organic materials and design of novel device structures, hybrid SCs based on n-type Si substrate achieved η higher than 16%,^{1401,1402} (record value of 17.4%).¹⁴⁰³ Despite the aforementioned results, the η value of hybrid SCs is still insufficient to compete with conventional inorganic Si SCs and PSCs (Section 6). Moreover, the stability of hybrid SCs is also limited compared to conventional inorganic PV technology.^{1404–1407} These drawbacks are strongly hindering the commercialization of hybrid SCs at a large scale. In this context, the incorporation of GRMs can help resolve both η and stability limits of hybrid SCs. For example, RGO has been proposed to produce a buffer layer in hybrid SCs to improve the light-induced charge extraction of $\sim 50\%$, as well as to replace the PEDOT:PSS contact.¹⁴⁰⁸ Recently, GQDs were mixed with PEDOT to be used in hybrid SCs using PEDOT:GQDs/porous Si/n-Si/TiO_x structure.¹⁴⁰⁹ In detail, GQDs improved the conductivity of PEDOT, porous Si reduced the overall reflectivity, and TiO_x acted as a passivation layer to reduce the recombination layer.¹⁴⁰⁸ The as-produced devices reached a maximum η value of 10.49%, retaining 78% of the initial η under ambient conditions for 15 days.¹⁴⁰⁸ GQDs, produced through a top-down strategy based on laser fragmentation in a post-hydrothermal treatment, were also used as a buffer layer between TiO₂ and P3HT to form a cascade energy-level scheme in hybrid SCs.¹⁴¹⁰ The introduction of GQDs into a BHJ hybrid SC led to the enhancement of η from 2.04% to 3.16%.¹⁴⁰⁹

Although the aforementioned examples demonstrated the potential of GRMs in hybrid SCs, further studies are needed to



formulate 2D materials in overcoming the fundamental issues exhibited by such type of SCs. Both progresses of 2D material science and hybrid SC-related technology could help for an in-depth reconsideration of 2D material-enabled hybrid SCs.

8. Outlook and conclusions

Several progresses have been achieved in the use of graphene and related 2D materials (GRMs) in solution-processed PVs. Regarding TCE applications, the implementation of solution-processed 2D materials is still at a premature stage. In fact, solution-processed graphene-based films typically exhibit sheet resistance (R_s) values in the order of $\text{k}\Omega \text{ sq}^{-1}$ (for $T_r \geq 80\%$),¹⁴¹¹ which are significantly higher than typical benchmarks (e.g., less than $\text{k}\Omega \text{ sq}^{-1}$ for ITO and FTO films). The origin of such low performance is mainly ascribed to the low lateral size of the liquid-phase exfoliated graphene flakes (typically in the order of few micrometers for high-quality graphene flakes)³⁵⁹ and the high contact resistance between the graphene flakes composing the electrode. However, the development of hybrids between solution-processed graphene and metal nanowires or CNTs, as well as the use of micromesh structures on top of the graphene-based films, represent promising approaches to overcome the current limitations. Prospectively, they could allow the design/realization of TCEs compatible with R2R large-area manufacturing. However, the high cost of metal nanowires¹⁴¹² (several hundreds of dollars per kilogram),¹⁴¹³ CNTs (even more than $1000 \text{ \$ kg}^{-1}$ for single-walled CNTs)¹⁴¹⁴ and microscale metal grids ($\$30\text{--}40 \text{ m}^{-2}$)¹⁴¹¹ is not lower than the cost of ITO ($\$5 \text{ m}^{-2}$ for a film with R_s of $150 \Omega \text{ sq}^{-1}$ films and higher than $\$20 \text{ m}^{-2}$ for films with R_s of $10 \Omega \text{ sq}^{-1}$,¹⁴¹⁵ or $600 \text{ \$ kg}^{-1}$),¹⁴¹⁶ making currently available graphene-based TCEs not competitive for massive use in large-area PV devices. Recently, transparent electrodes have also been demonstrated by spin coating 2D Ti_3C_2 from an aqueous dispersion for photodetector applications.¹⁴¹⁷ However, as for the case of solution-processed graphene, such a transparent electrode shows high sheet resistance, still being ineffective in collecting current density in the order of tens of milliamperes, as those displayed by PV devices. In addition, it should be noted that 2D materials have been used to develop efficient, transparent CE for bifacial DSSCs, which emerged as interesting systems for both BIPVs and tandem SCs.^{878–880,889}

The most successful applications of GRMs in PV technologies rely on their use in the form of CTLs for both holes and electrons (or interlayers in tandem PV architectures). For example, GRMs effectively act as dopants to improve the properties of traditional CTLs. The amount of GRMs needed for this purpose is often minimal, in the order of few weight (volume) percentages of the overall material (dispersion). For example, just 1.6 mL of graphene flakes dispersion at a concentration of 1 g L^{-1} is sufficient to realize 1 m^2 of advanced ETLs for PSCs.^{1107,1192,1273} By considering η higher than 18% in single-junction SCs,^{1107,1192} and even higher than 25% in tandem SCs,¹²⁷³ only a few grams of graphene flakes are needed for the realization of a 1 MWp PV plant. This amount of graphene flakes corresponds to a negligible

added marginal cost, in the order of tens of dollars per megawatts-peak.^{205,328,359} Thus, the integration of graphene and other metallic 2D materials,¹⁴¹⁸ including group-5 TMDs (e.g., TaS_2 , TaSe_2 , NbS_2 , NbSe_2 , VS_2 , VSe_2 , etc.), group-6 TMDs (e.g., the 1T polytype of MoS_2 and WS_2), topological insulators (e.g., Bi_2S_3 , Bi_2Se_3 , and Bi_2Te_3), and MXenes, as dopants in the CTL is an approach that can be immediately implemented on different solution-processed PV technologies at the industrial scale, without increasing the overall costs. Beyond their use as dopants, GRMs have been successfully used for the realization of a thin buffer layer (or interlayer) to improve the extraction/collection of the charge photogenerated in the photoactive layer of the cells toward the CTLs and current collectors. In this context, several studies have focused on the formulation of 2D material dispersions in solvents compatible with other materials composing the SC structure. For example, 2D TMD inks have been formulated in 2-propanol to be deposited as a buffer layer over the perovskite layer for the realization of PSCs, showing η exceeding 20%. Therefore, the incorporation of 2D material-based buffer layers into the most advanced SC architectures is highly promising to further boost the η value of PV technologies beyond the current record-high values. In addition, 2D material-based buffer layers can have a tangible impact on the enhancement of the long-term stability of SCs, particularly for OSCs and PSCs. In fact, 2D materials intrinsically act as shielding layers against humidity, offering promising potential as oxygen/moisture barriers. Moreover, they can also provide effective barriers against ion migration, stabilizing the photoactive perovskite layers or blocking metal/ion migration effects, which determines the degradation of PV devices. With regard to dopants, the amount of 2D materials required for the realization of thin films of 2D materials can be minimal, allowing almost zero additional costs. Not by chance, TMD-based buffer layers (e.g., MoS_2) have been used by research groups comprising authors of this work to build a 2D material-enabled solar farm (Fig. 26), without any significant impact over the technology lifecycle assessment (LCA) (data unpublished but reviewed by the European Commission in the context of the Graphene Flagship project).¹²⁹⁰

Another prospective application of 2D materials in solution-processed SCs is their use as additives in photoactive layers. In particular, the use of GRMs as energy cascade materials can increase the solar-light absorption, whilst eliminating charge recombination pathways occurring in the native materials. In addition, 2D materials can alter the interfacial properties of the photoactive material in contact with other materials composing the SC structure. Such effects can be used to improve charge transfer toward the CTLs (or current collectors), as recently shown with MXenes.¹¹²⁵ Therefore, the implementation of 2D material-based buffer layers has higher potential for boosting the PV performance of 3rd-generation SCs toward commercially competitive values. To accomplish these, the chemical functionalization of GRMs can be a key step to tune on-demand their optoelectronic properties, thereby adequately matching their energy levels with those of the active materials and CTLs. In addition to GRMs, 2D perovskites have been recently established to improve the thermal stability of PSCs,¹⁰⁴⁰ demonstrating that



rational perovskite engineering can advantageously regulate the structural, physical, and energetic properties of 2D/3D interfaces for the realization of efficient and stable PSCs.¹¹¹ Thus, the impact of 2D materials on the structural and optoelectronic properties of the photoactive layer represents a current “hot topic” for the future optimization of current state-of-the-art SCs. Even though the success of solution-processed 2D materials has been established in several PV technologies, we notice that major efforts are currently focused on PSCs, probably because of their attracting η exceeding 25%, together with their advantageous combination with Si SCs in tandem systems. In this context, the use of solution-processed 2D materials combined with advanced strategies proposed for optimizing the photoactive layer formulation and processing, as well as for device structure engineering, is promising to boost the η of SCs beyond the current state-of-the-art values. The same approach is also viable in enabling similar performance over large-area systems (from a module up to a solar farm). Moreover, the outcomes consolidated for PV technologies discussed in this work could also be extended to other types of thin-film SCs and Si SCs, in which the implementation of solution-processed 2D materials is still premature. Overall, we do believe that the conscious use of the ever-growing 2D materials portfolio can renew the expectation for the rapid establishment of advanced PV technologies worldwide. To accomplish these advances, the standardization of the morphological and structural characterization of 2D materials is crucial for the establishment of industrial-scale technologies, which also requires the setting up of reliable 2D material suppliers with a massive production capability. In this context, the recent standardization sequence of methods for characterizing the structural properties of graphene, bilayer graphene, and graphene nanoplatelets (ISO/TS 21356-1:2021) represents a step forward toward the upscaling of solution-processed 2D material-enabled SCs. Meanwhile, emerging solution-processed 2D materials, such as nonlayered materials, carbon nitrides (C_xN_y), 2D c-MOFs, layered double hydroxides, and other poorly investigated GRMs (*e.g.*, metal monochalcogenides, group-4 and group-5 TMDs, and polar and/or ferroelectric non-centrosymmetric materials) represent a playground for the realization of cutting-edge concepts of SCs.

Abbreviations

2D c-MOF	Two-dimensional conjugated metal–organic framework
AFM	Atomic force microscopy
AgNWs	Silver nanowires
ALD	Atomic layer deposition
ANIGQDs	Aniline graphene quantum dots
APjet	Atmospheric plasma jet
a-Si	Amorphous silicon
α	Optical absorption coefficient
α_{vis}	Optical absorption coefficient in the visible spectrum
BCP	Bathocuproine
BHJ	Bulk heterojunction

BIPVs	Building-integrated photovoltaics
BP	Black phosphorus
BPNFs	Black phosphorus nanoflakes
BPQDs	Black phosphorous quantum dots
CCG	Chemically converted graphene
CB	Conduction band
CE	Counter electrode
CIGS	Copper indium gallium diselenide
CIGSSe	Copper indium gallium selenide sulfide
C-PSC	Carbon perovskite solar cell
CQDs	Carbon quantum dots
CZTSe	Copper zinc tin sulfur-selenide alloy
CNTs	Carbon nanotubes
c-Si	Crystalline silicon
CTAB	Cetyl-trimethyl-ammonium-bromide
CV	Cyclic voltammetry
CVD	Chemical vapor deposition
D_n	Electron diffusion coefficient
DGU	Density gradient ultracentrifugation
DSSC	Dye-sensitized solar cell
δ_p	Optical penetration depth
ECS	Energy conversion and storage
EDNB	Ethylenediamine dinitrobenzoyl
e	Elementary charge
e^-	Electron
E_F	Fermi energy level
E_g	Optical bandgap
E_{ph}	Photon energy
EIS	Electrochemical impedance spectroscopy
EpD	Electrophoretic deposition
EQE	External quantum efficiency
ETLs	Electron transporting layers
e-graphene	Electrochemically exfoliated graphene
FA	HC(NH ₂) ₂
FF	Fill factor
FGSSs	Functionalized graphene sheets
fMoS ₂	Functionalized molybdenum disulfide
FoM	Figures of merit
FRGO	Fluorinated reduced graphene oxide
FTO	Fluorine-doped tin oxide
ϕ_w	Work function
GMO	Graphene-molybdenum disulfide heterostructure
GNPs	Graphene nanoplatelets
GNSSs	Graphene nanosheets
GNRs	Graphene nanoribbons
GO	Graphene oxide
GO-EDNB	Graphene oxide functionalized with ethylenediamine's amino groups
GO-TPP	Graphene oxide linked with porphyrin moieties
GO-Cl	Chlorinated graphene oxide
GQDs	Graphene quantum dots
GRMs	Graphene-related materials
GSs	Graphene sheets
h-BN	Hexagonal boron nitride
HIT	Heterojunction with intrinsic thin layer
HOMO	Highest occupied molecular orbital



HTLs	Hole transporting layers	PEAI	Phenethylammonium iodide
HSN	Hierarchically structured nanoparticles	(PEA) ₂ PbI ₄	Phenyl ethyl ammonium lead iodide
η	Solar-to-electrical energy conversion efficiency	P_{in}	Power of incident light
h^+	Hole	PC ₆₁ BM	[6,6]-Phenyl-C ₆₁ -butyric acid methyl ester
h	Planck's constant	PC ₇₁ BM	[6,6]-Phenyl-C ₇₁ -butyric acid methyl ester
\hbar	Reduced Planck's constant	PCDTBT	PC ₇₁ BM:poly[N-9'-heptadecanyl-2,7-carbazole- <i>alt</i> -5,5-(4',7'-di-2-thienyl-2',1',3'-benzothiadiazole)]:[6,6]-phenyl-C ₇₁ -butyric acid methyl ester
I	Electrical current		<i>N,N</i> -Dimethyl-ammonium <i>N</i> -oxide)propyl perylene diimide
ICBA	Indene-C ₆₀ bisadduct	PDINO	Graphene doped with <i>N,N</i> -dimethyl-ammonium <i>N</i> -oxide)propyl perylene diimide
ICLS	Interconnection layers	PDINO-G	Polydimethylsiloxane
IGO	Imidazole-functionalized GO	PDMS	Poly(3,4-ethylenedioxythiophene) polystyrene sulfonate
I_{MPP}	Current at the maximum power point	PEDOT:PSS	Poly(ethylene terephthalate)
I_{SC}	Short-circuit current	PET	Poly((9,9-bis(3'-(<i>N,N</i> -dimethylamino)propyl)-2,7-fluorene)- <i>alt</i> -2,7-(9,9-dioctylfluorene))
IQE	Internal quantum efficiency	PFN	Poly9,9-bis6-(<i>N,N,N</i> -trimethylammonium)hexyl-fluorene- <i>alt</i> -co-phenylenebromide
ITO	Indium-tin oxide	PFN-Br	Poly(3-hexylthiophene)
k_{B}	Boltzmann's constant	P3HT	Poly(3-hexylthiophene):[6,6]-phenyl C ₆₁ -butyric acid methyl ester
κ	Molar extinction coefficient	P3HT:PC ₆₁ BM	Poly(3-octylthiophene-2,5-diyl
LCOE	Levelized cost of energy	P3OT	Poly(3,4-ethylenedioxythiophene):poly(styrenesulfonate)
Li-TFSI	Lithium bis(trifluoromethanesulfonyl)imide	PH1000	Polymethyl methacrylate
LPE	Liquid phase exfoliation	PMMA	Poly[[4,8-bis[5-(2-ethylhexyl)-4-fluoro-2-thienyl]benzo[1,2- <i>b</i> :4,5- <i>b'</i>]dithiophene-2,6-diyl]-2,5-thiophenediyl[5,7-bis(2-ethylhexyl)-4,8-dioxo-4 <i>H</i> ,8 <i>H</i> -benzo[1,2- <i>c</i> :4,5- <i>c'</i>]dithiophene-1,3-diyl]-2,5-thiophenediyl]
LRGO	Laser-treated reduced graphene oxide	PM6	Thieno[3,4- <i>b</i>]thiophene/benzodithiophene:phenyl-C ₇₁ -butyric acid methyl ester
LUMO	Lowest unoccupied molecular orbital		Poly(triaryl)amine
λ	Photon wavelength	PTB7:PCB ₇₁ M	Partially reduced graphene oxide
MA	CH ₃ NH ₃		Perovskite solar cells
MBE	Molecular beam epitaxy		Perovskite solar modules
MEH-PPV	Poly[2-methoxy-5-(2'-ethylhexyloxy)-p-phenylene vinylene]		Photovoltaic
MGO	Multilayer graphene oxide		Quantum dots
MIR	Mid-infrared		Quantum dot-based dye sensitized solar cells
MLG	Multilayer graphene		Quantum dot solar cells
MOF	Metal-organic framework		Quantum dot-sensitized solar cells
MPA	3-Mercaptopropionic acid		Roll-to-roll
MPPT	Maximum power point		Charge transfer resistance
mTiO ₂	Mesoporous TiO ₂		Sheet resistance
MWCNTs	Multiwalled carbon nanotubes		Transport resistance of electrons in the TiO ₂ film
μ	Charge carrier mobility		Resistance at transparent conductive oxide/TiO ₂ contact
μ_{e}	Electron mobility		Charge transfer resistance of the charge recombination between electrons in the TiO ₂ film and I ₃ ⁻ in the electrolyte
μ_{h}	Hole mobility		Charge transfer resistance at the counter electrode/electrolyte interface
N_{d}	Charge carrier density		Charge transfer resistance at the TCO/electrolyte interface
n_{film}	Film refractive index		
n_{sub}	Substrate refractive index		
η_{th}	Theoretical solar-to-electrical energy conversion efficiency		
NFA	Non-fullerene acceptors		
NG/NiO	N-Doped graphene@nickel oxide		
N-GFs	N-Doped graphene frameworks		
NGNP	N-Doped graphene nanoplatelets		
NP	Nanoparticles		
NG	Amino-functionalized graphene		
NIR	Near-infrared		
NR	Nanorods		
NRGO	Nitrogen-doped reduced graphene oxide		
OLED	Organic light-emitting diodes		
O-MoS ₂	Oxygen-incorporated molybdenum disulfide		
OSCs	Organic solar cells		
OTR	Oxygen transmission rate		
oxo-G	Organo-sulfonate graphene		



RGO	Reduced graphene oxide
RGOMM	Reduced graphene oxide micromesh
rGS	Reduced graphene scaffold
RH	High humidity environment
RT	Room temperature
S-Q	Shockley-Queisser
SBS	Sedimentation-based separation
SCs	Solar cells
SLG	Single-layer graphene
Spiro-OMeTAD	2,2',7,7'-Tetrakis[N,N-di(4-methoxyphenyl)amino]-9,9'-spirobifluorene
SSA	Specific surface area
SWCNT	Single-walled carbon nanotube
σ	Electrical conductivity
σ_{dc}	d.c. conductivity
σ_{opt}	Optical conductivity
t	Photoactive material thickness
TBP	Tert-butylpyridine
TCEs	Transparent conductive electrodes
TCOs	Transparent conductive oxides
TCPP	Tetrakis(4-carboxyphenyl)porphyrin
TEGr	Thermally exfoliated graphene
TEM	Transmission electron microscopy
TFSCs	Thin-film solar cells
TFSI	Trifluoromethanesulfonyl imide
TMD	Transition metal dichalcogenide
ToF-SIMS	Time-of-flight secondary ion mass spectrometry
T_r	Optical transmittance
TRGO	Thermally reduced GO
TSHBC	Perthiolated tri-sulfur-annulated hexa-peri-hexabenzocoronene
τ	Electron lifetime
UVO	UV-ozone
VB	Valence band
V_{MPP}	Voltage at the maximum power point
V_{OC}	Open-circuit voltage
WVTR	Water vapor transmission rate
WJM	Wet-jet milling
XPS	X-ray photoelectron spectroscopy
XRD	X-ray diffraction
Z	Vacuum impedance
Z_d	Warburg impedance
ZnP	Zn-porphyrin
ZSO	Zinc stannate

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This project has received funding from the European Union's Horizon 2020 research and innovation program under grant agreements No. 785219 and 881603-GrapheneCore2 and GrapheneCore3, the MSCA-ITN ULTIMATE project under grant

agreement No. 813036, European Union's SENSIBAT project under grant agreement No. 957273, and the Bilateral project GINSENG between NSFC (China) and MAECI (Italy) (2018–2020), by the Natural Science Foundation of Shandong Province (ZR2019QEM009). ADC acknowledges the financial support of the Ministry of Education and Science of the Russian Federation in the framework of Megagrant No. 14.Y26.31.0027. G. G. acknowledges the “HY-NANO” project that has received funding from the European Research Council (ERC) Starting Grant 2018 under the European Union's Horizon 2020 research and innovation programme (Grant agreement No. 802862) and the project Cariplo Economia Circolare 2021 FLHYPER (num. 2020-1067).

References

- 1 S. H. Zaferani, in *Environmental Science & Engineering*, Studium Press LLC Publisher, Houston, USA, 2017, 9(7), 192–213.
- 2 S. D. Pohekar and M. Ramachandran, *Renewable Sustainable Energy Rev.*, 2004, **8**, 365–381.
- 3 S. Chu and A. Majumdar, *Nature*, 2012, **488**, 294.
- 4 Z. L. Wang and W. Wu, *Angew. Chem., Int. Ed.*, 2012, **51**, 2–24.
- 5 E. Pomerantseva, F. Bonaccorso, X. Feng, Y. Cui and Y. Gogotsi, *Science*, 2019, **366**, 6468.
- 6 W. Li, J. Liu and D. Zhao, *Nat. Rev. Mater.*, 2016, **1**, 1–17.
- 7 J. Antonanzas, N. Osorio, R. Escobar, R. Urraca, F. J. Martinez-de-Pison and F. Antonanzas-Torres, *Sol. Energy*, 2016, **136**, 78–111.
- 8 S. Sinha and S. S. Chandel, *Renewable Sustainable Energy Rev.*, 2015, **50**, 755–769.
- 9 T. D. Lee and A. U. Ebong, *Renewable Sustainable Energy Rev.*, 2017, **70**, 1286–1297.
- 10 S. Sharma, K. K. Jain and A. Sharma, *Mater. Sci. Appl.*, 2015, **6**, 1145.
- 11 R. Singh and G. F. Alapatt, *Proc. SPIE 8482*, 2012, **848205**, 928058.
- 12 L. El Chaar and N. El Zein, *Renewable Sustainable Energy Rev.*, 2011, **15**, 2165–2175.
- 13 V. A. Zuev and V. G. Litovchenko, *Phys. Status Solidi B*, 1966, **16**, 751–760.
- 14 J. J. Loferski, *J. Appl. Phys.*, 1956, **27**, 777–784.
- 15 B. Parida, S. Iniyar and R. Goic, *Renewable Sustainable Energy Rev.*, 2011, **15**, 1625.
- 16 G. K. Singh, *Energy*, 2013, **53**, 1–13.
- 17 M. A. Green, *Solar cells: operating principles, technology, and system applications*, Prentice-Hall, Upper Saddle River, New Jersey, 1982.
- 18 W. Shockley and H. J. Queisser, *J. Appl. Phys.*, 1961, **32**, 510–519.
- 19 <http://www.thesolarspark.co.uk/the-science/solar-power/tandem-solar-cells>, (accessed on March 2021).
- 20 J. Y. Kim, K. Lee, N. E. Coates, D. Moses, T.-Q. Nguyen, M. Dante and A. J. Heege, *Science*, 2007, **317**, 222–225.
- 21 L. Dou, J. You, J. Yang, C.-C. Chen, Y. He, S. Murase, T. Moriarty, K. Emery, G. Li and Y. Yang, *Nat. Photonics*, 2012, **6**, 180–185.



- 22 D. König, K. Casalenuovo, Y. Takeda, G. Conibeer, J. F. Guillemoles, R. Patterson, L. M. Huang and M. A. Green, *Physica E*, 2010, **42**, 2862–2866.
- 23 D. J. Farrell, Y. Takeda, K. Nishikawa, T. Nagashima, T. Motohiro and N. J. Ekins-Daukes, *Appl. Phys. Lett.*, 2011, **9**, 111102.
- 24 J. E. Murphy, M. C. Beard, A. G. Norman, S. P. Ahrenkiel, J. C. Johnson, P. Yu, O. I. Micic, R. J. Ellingson and A. J. Nozik, *J. Am. Chem. Soc.*, 2006, **128**, 3241–3247.
- 25 M. C. Beard, K. P. Knutsen, P. Yu, J. M. Luther, Q. Song, W. K. Metzger, R. J. Ellingson and A. J. Nozik, *Nano Lett.*, 2007, **7**, 2506–2512.
- 26 H. J. Queisser, *Sol. Energy Mater. Sol. Cells*, 2010, **94**, 1927–1930.
- 27 A. S. Brown, M. A. Green and R. P. Corkish, *Physica E*, 2002, **14**, 121–125.
- 28 M. A. Green, *Third Generation of Photovoltaic-Advanced solar energy conversion*, Springer-Verlag, Berlin Heidelberg, 2006.
- 29 D. Chapin, C. Fuller and G. Pearson, *J. Appl. Phys.*, 1954, **25**, 676.
- 30 http://solarcellcentral.com/markets_page.html, (accessed on June 2021).
- 31 M. A. Green, K. Emery, Y. Hishikawa, W. Warta and E. D. Dunlop, *Prog. Photovolt.: Res. Appl.*, 2013, **21**, 827–837.
- 32 K. Masuko, M. Shigematsu, T. Hashiguchi, D. Fujishima, M. Kai, N. Yoshimura, T. Yamaguchi, Y. Ichihashi, T. Mishima, N. Matsubara, T. Yamanishi, T. Takahama, M. Taguchi, E. Maruyama and S. Okamoto, *IEEE J. Photovolt.*, 2014, **4**, 1433–1435.
- 33 K. Yoshikawa, H. Kawasaki, W. Yoshida, T. Irie, K. Konishi, K. Nakano, T. Uto, D. Adachi, M. Kanematsu, H. Uzu and K. Yamamoto, *Nat. Energy*, 2017, **2**, 17032.
- 34 T. Kato, J. L. Wu, Y. Hirai, H. Sugimoto and V. Bermudez, *IEEE J. Photovolt.*, 2018, **9**, 325–330.
- 35 V. Fthenakis, *Renewable Sustainable Energy Rev.*, 2009, **13**, 2746–2750.
- 36 L. M. Peter, *Philos. Trans. R. Soc., A*, 2011, **369**, 1840–1856.
- 37 A. Goetzberger, C. Hebling and H.-W. Schock, *Mater. Sci. Eng., R*, 2003, **40**, 1–46.
- 38 D. Carlsson and C. Wonski, *Appl. Phys. Lett.*, 1976, **28**, 671–673.
- 39 G. J. Bauhuis, P. Mulder, E. J. Haverkamp, J. C. C. M. Huijben and J. J. Schermer, *Sol. Energy Mater. Sol. Cells*, 2009, **93**, 1488–1491.
- 40 R. Scheer and H.-W. Schock, *Chalcogenide Photovoltaics: Physics, Technologies, and Thin Film Devices*, Wiley-VCH, Berlin, 2011.
- 41 N. Khoshsirat, N. A. Md Yunus, M. N. Hamidona, S. Shafiea and N. Amin, *Optik*, 2015, **126**, 681–686.
- 42 J. M. Delgado-Sanchez, J. M. Lopez-Gonzalez, A. Orpella, E. Sanchez-Cortezon, M. D. Alba, C. Lopez-Lopez and R. Alcubilla, *Renewable Energy*, 2017, **101**, 90–95.
- 43 A. Goetzberger, C. Hebling and H.-W. Schock, *Mater. Sci. Eng., R*, 2003, **40**, 1–46.
- 44 P. P. Horley, L. L. Jiménez, S. A. Pérez García, J. Á. Quintana, Y. V. Vorobiev, R. R. Bon, V. P. Makhniy and J. G. Hernández, in *Application of Solar Energy*, ed. R. Rugescu, InTech, London, 2013, vol. 4, pp. 95–193.
- 45 F.-I. Lai, J.-F. Yang, Y.-L. Wei and S.-Y. Kuo, *Green Chem.*, 2017, **19**, 795–802.
- 46 S. Rühle, Tabulated values of the Shockley–Queisser limit for single junction solar cells, *Sol. Energy*, 2016, **130**, 139–147.
- 47 M. A. Green, A. Ho-Baillie and H. J. Snaith, *Nat. Photonics*, 2014, **8**, 506–514.
- 48 P. K. Nayak and D. Cahen, in *Advanced concepts in Photovoltaic*, ed. A. J. Nozik, G. Conibeer and M. C. Beard, The Royal Society of Chemistry, Cambridge, 2014, vol. 17, pp. 547–566.
- 49 A. Shah, P. Torres, R. Tscharnner, N. Wyrsh and H. Keppner, *Science*, 1999, **285**, 692–698.
- 50 P. Jackson, R. Wuerz, D. Hariskos, E. Lotter, W. Witte and M. Powalla, *Phys. Status Solidi RRL*, 2016, **10**, 583–586.
- 51 H. Hoppe and N. S. Sariciftci, *J. Mater. Res.*, 2004, **19**, 1925–1945.
- 52 B. O'Regan and M. Grätzel, *Nature*, 1991, **353**, 737–740.
- 53 G. Calogero, A. Bartolotta, G. Di Marco, A. Di Carlo and F. Bonaccorso, *Chem. Soc. Rev.*, 2015, **44**, 3244–3294.
- 54 K. Meng, G. Chen and K. R. Thampi, *J. Mater. Chem. A*, 2015, **3**, 23074–23089.
- 55 I. Gur, N. A. Fromer, M. L. Geier and A. P. Alivisatos, *Science*, 2005, **310**, 462–466.
- 56 X. Lan, S. Masala and E. H. Sargent, *Nat. Mater.*, 2014, **13**, 233–240.
- 57 O. E. Semonin, J. M. Luther and B. C. Matthew, *Mater. Today*, 2012, **15**, 508–515.
- 58 R. Plass, S. Pelet, J. Krueger, M. Grätzel and U. Bach, *J. Phys. Chem. B*, 2002, **106**, 7578–7580.
- 59 M. D. McGehee, *MRS Bull.*, 2009, **34**, 95–100.
- 60 M. Liu, M. B. Johnston and H. J. Snaith, *Nature*, 2013, **501**, 395–399.
- 61 M. A. Green, A. Ho-Baillie and H. J. Snaith, *Nat. Photonics*, 2014, **8**, 506–514.
- 62 F. Di Giacomo, V. Zardetto, A. D'Epifanio, S. Pescetelli, F. Matteocci, S. Razza, A. Di Carlo, S. Licocci, W. M. M. Kessels, M. Creatore and T. M. Brown, *Adv. Energy Mater.*, 2015, **5**, 1401808.
- 63 J. M. Martínez-Duart and J. Hernández-Moro, *J. Nanophotonics*, 2013, **7**, 078599.
- 64 J. P. Hansena, P. A. Narbelb and D. L. Aksnes, *Renewable Sustainable Energy Rev.*, 2017, **70**, 769–774.
- 65 Photovoltaic Report, Fraunhofer ISE, Freiburg, 12 July 2017, <http://www.ise.fraunhofer.de> (accessed on June 2021).
- 66 J. A. del Alamo, *Nature*, 2011, **479**, 317–323.
- 67 S. M. Sze and K. K. Ng, *Physics of semiconductor devices*, J. Wiley & Sons, Hoboken, USA, 2006.
- 68 M. Grundmann, *The Physics of Semiconductors: An Introduction Including Devices and Nanophysics*, Springer-Verlag, Berlin, Heidelberg, 2006.
- 69 K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, Y. Zhang, S. V. Dubonos, I. V. Grigorieva and A. A. Firsov, *Science*, 2004, **306**, 666–669.
- 70 A. K. Geim and K. S. Novoselov, *Nat. Mater.*, 2007, **6**, 183–191.



- 71 A. C. Ferrari, F. Bonaccorso, V. Fal'ko, K. S. Novoselov, S. Roche, P. R. Bøggild, S. Borini, F. H. L. Koppens, V. Palermo, N. Pugno, J. A. Garrido, R. Sordan, A. Bianco, L. Ballerini, M. Prato, E. Lidorikis, J. Kivioja, C. Marinelli, T. Ryhänen, A. Morpurgo, J. N. Coleman, V. Nicolosi, L. Colombo, A. Fert, M. Garcia-Hernandez, A. Bachtold, G. F. Schneider, F. Guinea, C. Dekker, M. Barbone, Z. Sun, C. Galiotis, A. N. Grigorenko, G. Konstantatos, A. Kis, M. Katsnelson, L. Vandersypen, A. Loiseau, V. Morandi, D. Neumaier, E. Treossi, V. Pellegrini, M. Polini, A. Tredicucci, G. M. Williams, B. H. Hong, J.-H. Ahn, J. M. Kim, H. Zirath, B. J. van Wees, H. van der Zant, L. Occhipinti, A. Di Matteo, I. A. Kinloch, T. Seyller, E. Quesnel, X. Feng, K. Teo, N. Rupesinghe, P. Hakonen, S. R. T. Neil, Q. Tannock, T. Löfwander and J. Kinaret, *Nanoscale*, 2015, **7**, 4587–5062.
- 72 S. Z. Butler, S. M. Hollen, L. Cao, Y. Cui, J. A. Gupta, H. R. Gutierrez, T. F. Heinz, S. S. Hong, J. Huang, A. F. Ismach, E. Johnston-Halperin, M. Kuno, V. V. Plashnitsa, R. D. Robinson, R. S. Ruoff, S. Salahuddin, J. Shan, L. Shi, M. G. Spencer, M. Terrones, W. Windl and J. E. Goldberger, *ACS Nano*, 2013, **7**, 2898–2926.
- 73 F. Bonaccorso, Z. Sun, T. Hasan and A. C. Ferrari, *Nat. Photonics*, 2010, **4**, 611.
- 74 M. D. Stoller, S. Park, Y. Zhu, J. An and R. S. Ruoff, *Nano Lett.*, 2008, **8**, 3498–3502.
- 75 S. Li, Z. Chen and W. Zhang, *Mater. Lett.*, 2012, **72**, 22–24.
- 76 G. T. Yue, J. H. Wu, Y. M. Xiao, M. L. Huang, J. M. Lin and J. Y. Lin, *J. Mater. Chem. A*, 2013, **1**, 1495–1501.
- 77 S. Y. Tai, C. J. Liu, S. W. Chou, F. S. S. Chien, J. Y. Lin and T. W. Lin, *J. Mater. Chem.*, 2012, **22**, 24753–24759.
- 78 Y. M. Han, B. Özyilmaz, Y. Zhang and P. Kim, *Phys. Rev. Lett.*, 2007, **98**, 206805.
- 79 L. Jiao, L. Zhang, X. Wang, G. Diankov and H. Dai, *Nature*, 2009, **458**, 877–880.
- 80 J. O. Sofo, A. S. Chaudhari and G. D. Barber, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2007, **75**, 153401.
- 81 H. P. Boehm, A. Clauss, G. Fischer and U. Hofmann, *Proceedings of the Fifth Conference on Carbon*, Pergamon, vol. 73, 1962.
- 82 C. Mattevi, G. Eda, S. Agnoli, S. Miller, K. A. Mkhoyan, O. Celik, D. Mastrogiorganni, G. Granozzi, E. Garfunkel and M. Chhowalla, *Adv. Funct. Mater.*, 2009, **19**, 2577.
- 83 F. Bonaccorso, A. Lombardo, T. Hasan, Z. Sun, L. Colombo and A. C. Ferrari, *Mater. Today*, 2012, **15**, 564.
- 84 D. Wickramaratne, F. Zahid and R. K. Lake, *J. Chem. Phys.*, 2014, **140**, 124710.
- 85 G. Eda, T. Fujita, H. Yamaguchi, D. Voiry, M. Chen and M. Chhowalla, *ACS Nano*, 2012, **6**, 7311–7317.
- 86 Q. H. Wang, K. Kalantar-Zadeh, A. Kis, J. N. Coleman and M. S. Strano, *Nat. Nanotechnol.*, 2012, **7**, 699–712.
- 87 O. V. Yazyev and A. Kis, *Mater. Today*, 2015, **18**, 20–30.
- 88 O. Lopez-Sanchez, D. Lembke, M. Kayci, A. Radenovic and A. Kis, *Nat. Nanotechnol.*, 2013, **8**, 497–501.
- 89 M.-R. Gao, Y.-F. Xu, J. Jiang and S.-H. Yu, *Chem. Soc. Rev.*, 2013, **42**, 2986–3017.
- 90 W. Choi, N. Choudhary, G. H. Han, J. Park, D. Akinwande and Y. H. Lee, *Mater. Today*, 2017, **20**, 116–130.
- 91 B. Martín-García, D. Spirito, S. Bellani, M. Prato, V. Romano, A. Polovitsyn, R. Brescia, R. Oropesa-Nuñez, L. Najafi, A. Ansaldò, G. D'Angelo, V. Pellegrini, R. Krahne, I. Moreels and F. Bonaccorso, *Small*, 2019, **15**, 1904670.
- 92 N. Balis, E. Stratakis and E. Kymakis, *Mater. Today*, 2016, **19**, 580–594.
- 93 S. Bellani, L. Najafi, A. Capasso, A. E. del Rio Castillo, M. R. Antognazza and F. Bonaccorso, *J. Mater. Chem. A*, 2017, **5**, 4384.
- 94 S. Bellani, L. Najafi, B. Martín-García, A. Ansaldò, A. E. Del Rio Castillo, M. Prato, I. Moreels and F. Bonaccorso, *J. Phys. Chem. C*, 2017, **121**, 21887.
- 95 L. Najafi, S. Bellani, R. Oropesa-Nuñez, B. Martín-García, M. Prato, L. Pasquale, J. K. Panda, P. Marvan, Z. Sofer and F. Bonaccorso, *ACS Catal.*, 2020, **10**, 3313–3325.
- 96 S. Zhao, T. Hotta, T. Koretsune, K. Watanabe, T. Taniguchi, K. Sugawara, T. Takahashi, H. Shinohara and R. Kitaura, *2D Mater.*, 2016, **3**, 025027.
- 97 H. Wang and X. Qian, *2D Mater.*, 2017, **4**, 015042.
- 98 L. C. Gomes and A. Carvalho, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2015, **92**, 085406.
- 99 M. Khazaei, A. Ranjbar, M. Arai, T. Sasaki and S. Yunoki, *J. Mater. Chem. C*, 2017, **5**, 2488–2503.
- 100 M. Naguib, V. N. Mochalin, M. W. Barsoum and Y. Gogotsi, *Adv. Mater.*, 2014, **26**, 992–1005.
- 101 H. Oughaddou, H. Enriquez, M. R. Tchalala, H. Yildirim, A. J. Mayne, A. Bendounan, G. Dujardin, M. A. Ali and A. Kara, *Prog. Surf. Sci.*, 2015, **90**, 46–83.
- 102 H. Liu, A. T. Neal, Z. Zhu, Z. Luo, X. Xu, D. Tománek and P. D. Ye, *ACS Nano*, 2014, **8**, 4033–4041.
- 103 C. Gibaja, D. Rodríguez-San-Miguel, P. Ares, J. Gómez-Herrero, M. Varela, R. Gillen, J. Maultzsch, F. Hauke, A. Hirsch, G. Abellán and F. Zamora, *Angew. Chem., Int. Ed.*, 2016, **55**, 14345.
- 104 E. Aktürk, O. Ü. Aktürk and S. Ciraci, *Phys. Rev. B*, 2016, **94**, 014115.
- 105 L. Lu, Z. Liang, L. Wu, Y. Chen, Y. Song, S. C. Dhanabalan, J. S. Ponraj, B. Dong, Y. Xiang, F. Xing and D. Fan, *Laser Photonics Rev.*, 2018, **12**, 1700221.
- 106 C. Kamal and M. Ezawa, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2015, **91**, 085423.
- 107 G. Li, Y. Li, H. Liu, Y. Guo, Y. Li and D. Zhu, *Chem. Commun.*, 2010, **46**, 3256–3258.
- 108 B. Li, C. Lai, M. Zhang, G. Zeng, S. Liu, D. Huang, L. Qin, X. Liu, H. Yi, F. Xu and N. An, *Adv. Energy Mater.*, 2020, **10**, 2000177.
- 109 Z. Zheng, J. Yao, J. Li and G. Yang, *Mater. Horiz.*, 2020, **7**, 2185–2207.
- 110 F. Zhang, H. Lu, J. Tong, J. J. Berry, M. C. Beard and K. Zhu, *Energy Environ. Sci.*, 2020, **13**, 1154–1186.
- 111 G. Grancini and M. K. Nazeeruddin, *Nat. Rev. Mater.*, 2019, **4**, 4–22.
- 112 Z. Liu, S. P. Lau and F. Yan, *Chem. Soc. Rev.*, 2015, **44**, 5638–5679.



- 113 V. Nicolosi, M. Chhowalla, M. G. Kanatzidis, M. S. Strano and J. N. Coleman, *Science*, 2013, **340**, 1420.
- 114 C. Backes, R. J. Smith, N. McEvoy, N. C. Berner, D. McCloskey, H. C. Nerl, A. O'Neill, P. J. King, T. Higgins, D. Hanlon, N. Scheuschner, J. Maultzsch, L. Houben, G. S. Duesberg, J. F. Donegan, V. Nicolosi and J. N. Coleman, *Nat. Commun.*, 2014, **5**, 4576.
- 115 J. Hassoun, F. Bonaccorso, M. Agostini, M. Angelucci, M. G. Betti, R. Cingolani, M. Gemmi, C. Mariani, S. Panero, V. Pellegrini and B. Scrosati, *Nano Lett.*, 2014, **14**, 4901.
- 116 A. A. Green and M. C. Hersam, *Nano Lett.*, 2009, **9**, 4031.
- 117 J. Kang, J.-W. T. Seo, D. Alducin, A. Ponce, M. J. Yacaman and M. C. Hersam, *Nat. Commun.*, 2014, **5**, 5478.
- 118 J. Zhu, J. Kang, J. Kang, D. Jariwala, J. D. Wood, J.-W. T. Seo, K.-S. Chen, T. J. Marks and M. C. Hersam, *Nano Lett.*, 2015, **15**, 7029–7036.
- 119 M. Chhowalla, H. S. Shin, G. Eda, L.-J. Li, K. P. Loh and H. Zhang, *Nat. Chem.*, 2013, **5**, 263–275.
- 120 Z. Sun, T. Hasan, F. Torrisi, D. Popa, G. Privitera, F. Wang, F. Bonaccorso, A. Basko and A. C. Ferrari, *ACS Nano*, 2010, **4**, 803.
- 121 J. Li, F. Ye, S. Vaziri, M. Muhammed, M. C. Lemme and M. Östling, *Adv. Mater.*, 2013, **25**, 3985.
- 122 E. B. Secor, B. Y. Ahn, T. Z. Gao, J. A. Lewis and M. S. Hersam, *Adv. Mater.*, 2015, **27**, 6683.
- 123 W. J. Hyun, E. B. Secor, M. C. Hersam, C. D. Frisbie and L. F. Francis, *Adv. Mater.*, 2015, **27**, 109.
- 124 K. Arapov, E. Rubingh, R. Abbel, J. Laven, G. de With and H. Friedric, *Adv. Funct. Mater.*, 2016, **26**, 586.
- 125 H. Sun, A. E. Del Rio Castillo, S. Monaco, A. Capasso, A. Ansaldo, M. Prato, D. A. Dinh, V. Pellegrini, B. Scrosati, L. Manna and F. Bonaccorso, *J. Mater. Chem. A*, 2016, **4**, 6886.
- 126 X. Wang, L. Zhi and K. Mullen, *Nano Lett.*, 2007, **8**, 323.
- 127 G. Eda, H. E. Unalan, N. Rupesinghe, G. A. J. Amaratunga and M. Chhowalla, *Appl. Phys. Lett.*, 2008, **93**, 233502.
- 128 E. Kymakis, E. Stratakis, M. M. Stylianakis, E. Koudoumas and C. Fotakis, *Thin Solid Films*, 2011, **520**, 1238.
- 129 P. Blake, P. D. Brimicombe, R. R. Nair, T. J. Booth, D. Jiang, F. Schedin, L. A. Ponomarenko, S. V. Morozov, H. Gleeson, E. W. Hill, A. K. Geim and K. S. Novoselov, *Nano Lett.*, 2008, **8**, 1704.
- 130 P. Cataldi, I. S. Bayer, F. Bonaccorso, V. Pellegrini, A. Athanassiou and R. Cingolani, *Adv. Electron. Mater.*, 2015, **1**, 1500224.
- 131 Z. Song, C. L. McElvany, A. B. Phillips, I. Celik, P. W. Krantz, S. C. Watthage, G. K. Liyanage, D. Apul and M. J. A. Heben, *Energy Environ. Sci.*, 2017, **10**, 1297–1305.
- 132 N. L. Chang, A. W. Y. Ho-Baillie, D. Vak, M. Gao, M. A. Green and R. J. Egan, *Sol. Energy Mater. Sol. Cells*, 2018, **174**, 314–324.
- 133 N. L. Chang, A. W. Yi Ho-Baillie, P. A. Basore, T. L. Young, R. Evans and R. J. A. Egan, *Prog. Photovolt.: Res. Appl.*, 2017, **25**, 390–405.
- 134 https://www.eia.gov/outlooks/aeo/pdf/electricity_generation.pdf (accessed on June 2021).
- 135 L. Lazard, *Lazard's Levelized Cost of Energy Analysis V13.0*, 2019.
- 136 E. H. Hwang, S. Adam and S. Das Sarma, *Phys. Rev. Lett.*, 2007, **98**, 186806.
- 137 F. Bonaccorso, L. Colombo, G. Yu, M. L. Stoller, V. Tozzini, A. C. Ferrari, R. S. Ruoff and V. Pellegrini, *Science*, 2015, **347**, 1246501.
- 138 D. A. C. Brownson and C. E. Banks, *Analyst*, 2010, **135**, 2768–2778.
- 139 M. Scarselli, P. Castrucci and M. De Crescenzi, *J. Phys.: Condens. Matter*, 2012, **24**, 313202.
- 140 E. Bourgeat-Lami, J. Faucheu and A. Noel, *Polym. Chem.*, 2015, **6**, 5323–5357.
- 141 N. M. R. Peres, *J. Phys.: Condens. Matter*, 2009, **21**, 323201.
- 142 Y. Zhu, S. Murali, W. Cai, X. Li, J. W. Suk, J. R. Potts and R. S. Ruoff, *Adv. Mater.*, 2010, **22**, 3906–3924.
- 143 J. Du and H. M. Cheng, *Macromol. Chem. Phys.*, 2012, **213**, 1060–1077.
- 144 R. J. Young, I. A. Kinloch, L. Gong and K. S. Novoselov, *Compos. Sci. Technol.*, 2012, **72**, 1459–1476.
- 145 H. Kim, A. A. Abdala and C. W. Macosko, *Macromolecules*, 2010, **43**, 6515–6530.
- 146 V. Chabot, D. Higgins, A. Yu, X. Xiao, Z. Chen and J. Zhang, *Energy Environ. Sci.*, 2014, **7**, 1564–1596.
- 147 D. Chen, H. Feng and J. Li, *Chem. Rev.*, 2012, **112**, 6027–6053.
- 148 A. K. Geim, *Science*, 2009, **324**, 1530–1534.
- 149 H.-X. Wang, Q. Wang, K.-G. Zhou and H.-L. Zhang, *Small*, 2013, **9**, 1266–1283.
- 150 K. I. Bolotina, K. J. Sikesb, Z. Jianga, M. Klimac, G. Fudenberg, J. Honec, P. Kima and H. L. Stormer, *Solid State Commun.*, 2008, **14**, 6351–6355.
- 151 T. Ando, *J. Phys. Soc. Jpn.*, 2006, **75**, 074716.
- 152 S. Adam, E. H. Hwang, V. Galitski and S. D. Sarma, *Proc. Natl. Acad. Sci. U. S. A.*, 2007, **104**, 18392.
- 153 S. Fratini and F. Guinea, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2008, **77**, 195415.
- 154 J.-H. Chen, C. Jang, S. Xiao, M. Ishigami and M. S. Fuhrer, *Nat. Nanotechnol.*, 2008, **3**, 206–209.
- 155 M. Ishigami, J. H. Chen, W. G. Cullen, M. S. Fuhrer and E. D. Williams, *Nano Lett.*, 2007, **7**, 1643–1648.
- 156 M. I. Katsnelson and A. K. Geim, *Philos. Trans. R. Soc., A*, 2007, **366**, 195–204.
- 157 S. V. Morozov, K. S. Novoselov, M. I. Katsnelson, F. Schedin, D. C. Elias, J. A. Jaszczak and A. K. Geim, *Phys. Rev. Lett.*, 2008, **100**, 016602.
- 158 G. Giovannetti, P. Khomyakov, G. Brocks, P. Kelly and J. V. D. Brink, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2007, **76**, 073103.
- 159 C. R. Dean, A. F. Young, I. Meric, C. Lee, L. Wang, S. Sorgenfrei, K. Watanabe, T. Taniguchi, P. Kim, K. L. Shepard and J. Hone, *Nat. Nanotechnol.*, 2010, **5**, 722–726.
- 160 W. Gannett, W. Regan, K. Watanabe, T. Taniguchi, M. F. Crommie and A. Zettl, *Appl. Phys. Lett.*, 2011, **98**, 242105.
- 161 X. Huang, Z. Zeng, Z. Fan, J. Liu and H. Zhang, *Adv. Mater.*, 2012, **24**, 5979–6004.



- 162 C. Xu, B. Xu, Y. Gu, Z. Xiong, J. Sun and X. S. Zhao, *Energy Environ. Sci.*, 2013, **6**, 1388–1414.
- 163 P. J. Mole, J. M. Rorison, J. A. del Alamo and D. Lancefield, in *Properties of crystalline silicon*, ed. R. Hull, Inspec, London UK, 1999.
- 164 Y. Zhao, C. Hu, Y. Hu, H. Cheng, G. Shi and L. Qu, *Angew. Chem., Int. Ed.*, 2012, **51**, 11371–11375.
- 165 Z. Chen, C. Xu, C. Ma, W. Ren and H. M. Cheng, *Adv. Mater.*, 2013, **25**, 1296–1300.
- 166 Y. He, W. Chen, X. Li, Z. Zhang, J. Fu, C. Zhao and E. Xie, *ACS Nano*, 2013, **7**, 174–182.
- 167 Y. Zhang, Y. Huang, T. Zhang, H. Chang, P. Xiao, H. Chen, Z. Huang and Y. Chen, *Adv. Mater.*, 2015, **27**, 2049–2053.
- 168 R. R. Nair, P. Blake, A. N. Grigorenko, K. S. Novoselov, T. J. Booth, T. Stauber, N. M. R. Peres and A. K. Geim, *Science*, 2008, **320**, 1308.
- 169 X. Li, Y. Zhu, W. Cai, M. Borysiak, B. Han, D. Chen, R. D. Piner, L. Colombo and R. S. Ruoff, *Nano Lett.*, 2009, **9**, 4359–4363.
- 170 G. R. Bhimanapati, Z. Lin, V. Meunier, Y. Jung, J. Cha, S. Das, D. Xiao, Y. Son, M. L. S. Strano, V. R. Cooper, L. Liang, S. G. Louie, E. Ringe, W. Zhou, S. S. Kim, R. R. Naik, B. G. Sumpter, H. Terrones, F. Xia, Y. Wang, J. Zhu, D. Akinwande, N. Alem, J. A. Schuller, R. E. Schaak, M. Terrones and J. A. Robinson, *ACS Nano*, 2015, **9**, 11509–11539.
- 171 A. Gupta, T. Sakthivel and S. Seal, *Prog. Mater. Sci.*, 2015, **73**, 44–126.
- 172 L. Najafi, S. Bellani, R. Oropesa-Nuñez, R. Brescia, M. Prato, L. Pasquale, C. Demirci, F. Drago, B. Martín-García, J. Luxa and L. Manna, *Small*, 2020, 2003372.
- 173 H. Beydaghi, L. Najafi, S. Bellani, A. Bagheri, B. Martín-García, P. Salarizadeh, K. Hooshyari, S. Naderizadeh, M. Serri, L. Pasquale, B. Wu, R. Oropesa-Nuñez, Z. Sofer, V. Pellegrini and F. Bonaccorso, *J. Mater. Chem. A*, 2021, **9**, 6368–6381.
- 174 L. Kou, Y. Ma, Z. Sun, T. Heine and C. Chen, *J. Phys. Chem. Lett.*, 2017, **8**, 1905–1919.
- 175 N. Xu, Y. Xu and J. Zhu, *npj Quantum Mater.*, 2017, **2**, 1–9.
- 176 K. F. Mak, C. Lee, J. Hone, J. Shan and T. F. Heinz, *Phys. Rev. Lett.*, 2010, **105**, 136805.
- 177 J. E. Padilha, H. Peelaers, A. Janotti and C. G. Van de Walle, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2014, **90**, 205420.
- 178 M. Mehboudi, B. M. Fregoso, Y. Yang, W. Zhu, A. van der Zande, J. Ferrer, L. Bellaiche, P. Kumar and S. Barraza-Lopez, *Phys. Rev. Lett.*, 2016, **117**, 246802.
- 179 M. I. Zappia, G. Bianca, S. Bellani, M. Serri, L. Najafi, R. Oropesa-Nuñez, B. Martín-García, D. Bouša, D. Sedmidubský, V. Pellegrini, Z. Sofer, A. Cupolillo and F. Bonaccorso, *Adv. Funct. Mater.*, 2019, **30**, 1909572.
- 180 G. Bianca, M. I. Zappia, S. Bellani, Z. Sofer, M. Serri, L. Najafi, R. Oropesa-Nuñez, B. Martín-García, T. Hartman, L. Leoncino and D. Sedmidubský, *ACS Appl. Mater. Interfaces*, 2020, **12**, 48598–48613.
- 181 M. Zappia, G. Bianca, S. Bellani, N. Curreli, Z. Sofer, M. Serri, L. Najafi, M. Piccinni, R. Oropesa-Nuñez, P. Marvan, V. Pellegrini, I. Kriegel, M. Prato, A. Cupolillo and F. Bonaccorso, *J. Phys. Chem. C*, 2021, **125**(22), 11857–11866.
- 182 K. Kalantar-zadeh, J. Z. Ou, T. Daeneke, A. Mitchell, T. Sasaki and M. S. Fuhrer, *Appl. Mater. Today*, 2016, **5**, 73.
- 183 S. Balendhran, S. Walia, H. Nili, S. Sriram and M. Bhaskaran, *Small*, 2015, **11**, 640.
- 184 N. R. Glavin, R. Rao, V. Varshney, E. Bianco, A. Apte, A. Roy, E. Ringe and P. M. Ajayan, *Adv. Mater.*, 2019, 1904302.
- 185 M. Naguib, V. N. Mochalin, M. W. Barsoum and Y. Gogotsi, *Adv. Mater.*, 2014, **26**, 992.
- 186 X. Li, L. Tao, Z. Chen, H. Fang, X. Li, X. Wang, J. B. Xu and H. Zhu, *Appl. Phys. Rev.*, 2017, **4**, 021306.
- 187 G. Iannaccone, F. Bonaccorso, L. Colombo and G. Fiori, *Nat. Nanotechnol.*, 2018, **13**, 183.
- 188 L. Najafi, S. Bellani, R. Oropesa-Nuñez, B. Martín-García, M. Prato, V. Mazánek, D. Debellis, S. Lauciello, R. Brescia, Z. Sofer and F. Bonaccorso, *J. Mater. Chem. A*, 2019, **7**, 25593–25608.
- 189 Z. Yin, J. Zhu, Q. He, X. Cao, C. Tan, H. Chen, Q. Yan and H. Zhang, *Adv. Energy Mater.*, 2014, **4**, 1300574.
- 190 K. S. Novoselov, A. Mishchenko, A. Carvalho and A. H. Castro Neto, *Science*, 2016, **29**, aac9439.
- 191 L. Britnell, R. M. Ribeiro, A. Eckmann, R. Jalil, B. D. Belle, A. Mishchenko, Y. J. Kim, R. V. Gorbachev, T. Georgiou, S. V. Morozov, A. N. Grigorenko, A. K. Geim, C. Casiraghi, A. H. Castro Neto and K. S. Novoselov, *Science*, 2013, **340**, 1311–1314.
- 192 G. W. Mudd, S. A. Svatek, L. Hague, O. Makarovskiy, Z. R. Kudrynskiy, C. J. Mellor, P. H. Beton, L. Eaves, K. S. Novoselov, Z. D. Kovalyuk, E. E. Vdovin, A. J. Marsden, N. R. Wilson and A. Patané, *Adv. Mater.*, 2015, **27**, 3760–3766.
- 193 P. Rivera, J. R. Schaibley, A. M. Jones, J. S. Ross, S. Wu, G. Aivazian, P. Klement, K. Seyler, G. Clark, N. J. Ghimire, J. Yan, D. G. Mandrus, W. Yao and X. Xu, *Nat. Commun.*, 2015, **6**, 6242.
- 194 H. Fang, C. Battaglia, C. Carraro, S. Nemsak, B. Ozdol, J. S. Kang, H. A. Bechtel, S. B. Desai, F. Kronast, A. A. Unal, G. Conti, C. Conlon, G. K. Palsson, M. C. Martin, A. M. Minor, C. S. Fadley, E. Yablonovitch, R. Maboudian and A. Javey, *Proc. Natl. Acad. Sci. U. S. A.*, 2014, **111**, 6198–6202.
- 195 F. Wang, Z. Wang, K. Xu, F. Wang, Q. Wang, Y. Huang, L. Yin and J. He, *Nano Lett.*, 2015, **15**, 7558–7566.
- 196 B. V. Lotsch, *Annu. Rev. Mater. Res.*, 2015, **45**, 85–109.
- 197 H. Wang, F. Liu, W. Fu, Z. Fang, W. Zhou and Z. Liu, *Nanoscale*, 2014, **6**, 12250–12272.
- 198 Y. Liu, N. O. Weiss, X. Duan, H. C. Cheng, Y. Huang and X. Duan, *Nat. Rev. Mater.*, 2016, **1**, 1–17.
- 199 A. Tartakovskii, *Nat. Rev. Phys.*, 2020, **2**, 8–9.
- 200 F. Withers, H. Yang, L. Britnell, A. P. Rooney, E. Lewis, A. Felten, C. R. Woods, V. Sanchez Romaguera, T. Georgiou, A. Eckmann and Y. J. Kim, *Nano Lett.*, 2014, **14**, 3987–3992.



- 201 X. Cai, T. C. Ozawa, A. Funatsu, R. Ma, Y. Ebina and T. Sasaki, *J. Am. Chem. Soc.*, 2015, **137**, 2844–2847.
- 202 D. McManus, S. Vranic, F. Withers, V. Sanchez-Romaguera, M. Macucci, H. Yang, R. Sorrentino, K. Parvez, S. K. Son, G. Iannaccone and K. Kostarelos, *Nat. Nanotechnol.*, 2017, **12**, 343–350.
- 203 T. Carey, S. Cacovich, G. Divitini, J. Ren, A. Mansouri, J. M. Kim, C. Wang, C. Ducati, R. Sordan and F. Torrisi, *Nat. Commun.*, 2017, **8**, 1–11.
- 204 M. M. Alsaif, S. Kuriakose, S. Walia, N. Syed, A. Jannat, B. Y. Zhang, F. Haque, M. Mohiuddin, T. Alkathiri, N. Pillai and T. Daeneke, *Adv. Mater. Interfaces*, 2019, **6**, 1900007.
- 205 F. Bonaccorso, A. Bartolotta, J. N. Coleman and C. Backes, *Adv. Mater.*, 2016, **28**, 6136.
- 206 S. Bellani, L. Najafi, P. Zani, B. Martín-García, R. Oropesa-Núñez and F. Bonaccorso, Electrically conductive adhesive, Pat. Nr., WO2020170154, 2020.
- 207 M. A. Garakani, S. Bellani, V. Pellegrini, R. Oropesa-Núñez, A. E. Del Rio Castillo, S. Abouali, L. Najafi, B. Martín-García, A. Ansaldi, P. Bondavalli, C. Demirci, V. Romano, E. Mantero, L. Marasco, M. Prato, G. Bracciale and F. Bonaccorso, *Energy Storage Mater.*, 2020, **34**, 1–11.
- 208 X. Huang, T. Leng, M. Zhu, X. Zhang, J. Chen, K. Chang, M. Aqeeli, A. K. Geim, K. S. Novoselov and Z. Hu, *Sci. Rep.*, 2015, **5**, 18298.
- 209 J. Li, F. Ye, S. Vaziri, M. Muhammed, M. C. Lemme and M. Östling, *Adv. Mater.*, 2013, **25**, 3985–3992.
- 210 F. Wang, Z. Wang, T. A. Shifa, Y. Wen, F. Wang, X. Zhan, Q. Wang, K. Xu, Y. Huang, L. Yin and C. Jiang, *Adv. Funct. Mater.*, 2017, **27**, 1603254.
- 211 N. Zhou, R. Yang and T. Zhai, *Mater. Today Nano*, 2019, **8**, 100051.
- 212 F. Wang, Z. Wang, Q. Wang, F. Wang, L. Yin, K. Xu, Y. Hunag and J. He, *Nanotechnology*, 2015, **26**, 292001.
- 213 P. Tao, S. Yao, F. Liu, B. Wang, F. Huang and M. Wang, *J. Mater. Chem. A*, 2019, **7**, 23512–23536.
- 214 Y. Wang, Z. Zhang, Y. Mao and X. Wang, *Energy Environ. Sci.*, 2020, **13**, 3993.
- 215 S. Liu, L. Xie, H. Qian, G. Liu, H. Zhong and H. Zeng, *J. Mater. Chem. A*, 2019, **7**, 15411–15419.
- 216 X. Zhang, Z. Zhang, J. Liang, Y. Zhou, Y. Tong, Y. Wang and X. Wang, *J. Mater. Chem. A*, 2017, **5**, 9702–9708.
- 217 L. Peng, P. Xiong, L. Ma, Y. Yuan, Y. Zhu, D. Chen, X. Luo, J. Lu, K. Amine and G. Yu, *Nat. Commun.*, 2017, **8**, 1–10.
- 218 N. Zhou, L. Gan, R. Yang, F. Wang, L. Li, Y. Chen, D. Li and T. Zhai, *ACS Nano*, 2019, **13**, 6297–6307.
- 219 H. Kaur, R. Tian, A. Roy, M. McCrystall, D. V. Horváth, G. Lozano Onrubia, R. Smith, M. Ruether, A. Griffin, C. Backes, V. Nicolosi and J. N. Coleman, *ACS Nano*, 2020, **14**, 13418–13432.
- 220 B. Li, L. Huang, M. Zhong, Z. Wei and J. Li, *RSC Adv.*, 2015, **5**, 91103–91107.
- 221 Y. Zhao, D. Yu, J. Lu, L. Tao, Z. Chen, Y. Yang, A. Wei, L. Tao, J. Liu, Z. Zheng, M. Hao and J. B. Xu, *Adv. Opt. Mater.*, 2019, **7**, 1901085.
- 222 H. Wu, X. Lu, G. Zheng and G. W. Ho, *Adv. Energy Mater.*, 2018, **8**, 1702704.
- 223 Y. Wang, H. Li, T. Yang, Z. Zou, Z. Qi, L. Ma and J. Chen, *Mater. Lett.*, 2019, **238**, 309–312.
- 224 M. Q. Yang, J. Dan, S. J. Pennycook, X. Lu, H. Zhu, Q. H. Xu, H. J. Fan and G. W. Ho, *Mater. Horiz.*, 2017, **4**, 885–894.
- 225 C. Gong, J. Chu, C. Yin, C. Yan, X. Hu, S. Qian, Y. Hu, K. Hu, J. Huang, H. Wang, Y. Wang, P. Wangyang, T. Lei, L. Dai, C. Wu, B. Chen, C. Li, M. Liao, T. Zhai and J. Xiong, *Adv. Mater.*, 2019, **31**, 1903580.
- 226 K. Yao, P. Chen, Z. Zhang, J. Li, R. Ai, H. Ma, B. Zhao, G. Sun, R. Wu, X. Tang and B. Li, *npj 2D Mater. Appl.*, 2018, **2**, 1–7.
- 227 A. A. Suleiman, P. Huang and B. Jin, *Adv. Electron. Mater.*, 2020, **6**, 2000284.
- 228 X. Hu, P. Huang, B. Jin, X. Zhang, H. Li, X. Zhou and T. Zhai, *J. Am. Chem. Soc.*, 2018, **140**, 12909–12914.
- 229 J. D. Yao, J. M. Shao and G. W. Yang, *Sci. Rep.*, 2015, **5**, 12320.
- 230 Q. Zhou, D. Lu, H. Tang, S. Luo, Z. Li, H. Li, X. Qi and J. Zhong, *ACS Appl. Electron. Mater.*, 2020, **2**, 1254–1262.
- 231 M. Amani, C. Tan, G. Zhang, C. Zhao, J. Bullock, X. Song, H. Kim, V. R. Shrestha, Y. Gao, K. B. Crozier, M. Scott and A. Javey, *ACS Nano*, 2018, **12**, 7253–7263.
- 232 T. Fan, Z. Xie, W. Huang, Z. Li and H. Zhang, *Nanotechnology*, 2019, **30**, 114002.
- 233 H. F. Liu, K. K. A. Antwi, N. L. Yakovlev, H. R. Tan, L. T. Ong, S. J. Chua and D. Z. Chi, *ACS Appl. Mater. Interfaces*, 2014, **6**, 3501–3507.
- 234 W. Huang, L. Gan, H. Yang, N. Zhou, R. Wang, W. Wu, H. Li, Y. Ma, H. Zeng and T. Zhai, *Adv. Funct. Mater.*, 2017, **27**, 1702448.
- 235 X. B. Li, P. Guo, Y. N. Zhang, R. F. Peng, H. Zhang and L. M. Liu, *J. Mater. Chem. C*, 2015, **3**, 6284–6290.
- 236 J. Wu, Z. Yang, C. Qiu, Y. Zhang, Z. Wu, J. Yang, Y. Lu, J. Li, D. Yang, R. Hao, E. Li, G. Yu and S. Lin, *Nanoscale*, 2018, **10**, 8023–8030.
- 237 R. Cheng, Y. Wen, L. Yin, F. Wang, F. Wang, K. Liu, T. A. Shifa, J. Li, C. Jiang, Z. Wang and J. He, *Adv. Mater.*, 2017, **29**, 1703122.
- 238 N. Li, Y. Zhang, R. Cheng, J. Wang, J. Li, Z. Wang, M. G. Sendeku, W. Huang, Y. Yao, Y. Wen and J. He, *ACS Nano*, 2019, **13**, 12662–12670.
- 239 Y. Wen, Q. Wang, L. Yin, Q. Liu, F. Wang, F. Wang, Z. Wang, K. Liu, K. Xu, Y. Huang, T. A. Shifa, C. Jiang, J. Xiong and J. He, *Adv. Mater.*, 2016, **28**, 8051–8057.
- 240 R. Chai, Y. Chen, M. Zhong, H. Yang, F. Yan, M. Peng, Y. Sun, K. Wang, Z. Wei, W. Hu, Q. J. Liu, Z. Lou and G. Shen, *J. Mater. Chem. C*, 2020, **8**, 6388–6395.
- 241 W. Feng, W. Zheng and P. A. Hu, *Phys. Chem. Chem. Phys.*, 2014, **16**, 19340–19344.
- 242 J. Yao, Z. Deng, Z. Zheng and G. Yang, *ACS Appl. Mater. Interfaces*, 2016, **8**, 20872–20879.
- 243 Q. Wang, K. Xu, Z. Wang, F. Wang, Y. Huang, M. Safdar, X. Zhan, F. Wang, Z. Cheng and J. He, *Nano Lett.*, 2015, **15**, 1183–1189.



- 244 H. Liu, M. Yu, F. Qin, W. Feng and P. A. Hu, *ACS Appl. Nano Mater.*, 2018, **1**, 5414–5418.
- 245 S. Kang, T. Dai, X. Ma, S. Dang, H. Li, P. Hu, F. Yu, X. Zhou, S. Wu and S. Li, *Nanoscale*, 2019, **11**, 1879–1886.
- 246 Y. Zhan, Z. Shao, T. Jiang, J. Ye, X. Wu, B. Zhang, K. Ding, D. Wu and J. Jie, *J. Mater. Chem. A*, 2020, **8**, 789–796.
- 247 R. Zhang, X. Ma, C. An, D. Zhang, D. Sun, X. Hu and J. Liu, *2D Mater.*, 2019, **6**, 035033.
- 248 H.-C. Zhou, J. R. Long and O. M. Yaghi, *Chem. Rev.*, 2012, **112**, 673.
- 249 J. Liu and C. Wöll, *Chem. Soc. Rev.*, 2017, **46**, 5730.
- 250 S. Yuan, L. Feng, K. Wang, J. Pang, M. Bosch, C. Lollar, Y. Sun, J. Qin, X. Yang, P. Zhang, Q. Wang, L. Zou, Y. Zhang, L. Zhang, Y. Fang, J. Li and H.-C. Zhou, *Adv. Mater.*, 2018, **30**, 1704303.
- 251 L. Sun, M. G. Campbell and M. Dincă, *Angew. Chem., Int. Ed.*, 2016, **55**, 3566.
- 252 L. S. Xie, G. Skorupskii and M. Dincă, *Chem. Rev.*, 2020, **120**, 8536.
- 253 M. Wang, R. Dong and X. Feng, *Chem. Soc. Rev.*, 2021, **50**, 2764–2793.
- 254 M. Ko, L. Mendecki and K. A. Mirica, *Chem. Commun.*, 2018, **54**, 7873.
- 255 K. Natarajan, A. K. Gupta, S. N. Ansari, M. Saraf and S. M. Mobin, *ACS Appl. Mater. Interfaces*, 2019, **11**, 13295–13303.
- 256 R. Dong, Z. Zhang, D. C. Tranca, S. Zhou, M. Wang, P. Adler, Z. Liao, F. Liu, Y. Sun, W. Shi and Z. Zhang, *Nat. Commun.*, 2018, **9**, 1–9.
- 257 J. Li and R. Wu, *Nanoscale*, 2020, **12**, 23620–23625.
- 258 J. Park, M. Lee, D. Feng, Z. Huang, A. C. Hinckley, A. Yakovenko, X. Zou, Y. Cui and Z. Bao, *J. Am. Chem. Soc.*, 2018, **140**, 10315.
- 259 K. Wada, K. Sakaushi, S. Sasaki and H. Nishihara, *Angew. Chem., Int. Ed.*, 2018, **57**, 8886.
- 260 D. Sheberla, J. C. Bachman, J. S. Elias, C. J. Sun, Y. Shao-Horn and M. Dincă, *Nat. Mater.*, 2017, **16**, 220.
- 261 D. Feng, T. Lei, M. R. Lukatskaya, J. Park, Z. Huang, M. Lee, L. Shaw, S. Chen, A. A. Yakovenko, A. Kulkarni, J. Xiao, K. Fredrickson, J. B. Tok, X. Zou, Y. Cui and Z. Bao, *Nat. Energy*, 2018, **3**, 30.
- 262 S. Wu, Z. Li, M. Q. Li, Y. Diao, F. Lin, T. Liu, J. Zhang, P. Tieu, W. Gao, F. Qi and X. Pan, *Nat. Nanotechnol.*, 2020, **15**, 934–940.
- 263 J. Ji, B. Liu, H. Huang, X. Wang, L. Yan, S. Qu, X. Liu, H. Jiang, M. Duang, Y. Li and M. Li, *J. Mater. Chem. C*, 2021, **9**, 7057.
- 264 L. Tan, C. Nie, Z. Ao, H. Sun, T. An and T. S. Wang, *J. Mater. Chem. A*, 2020, **9**, 17–33.
- 265 I. Inagaki, T. Tsumura, T. Kinumoto and M. Toyoda, *Carbon*, 2019, **141**, 580–607.
- 266 J. Wen, J. Xie, X. Chen and X. Li, *Appl. Surf. Sci.*, 2017, **391**, 72–123.
- 267 J. Mahmood, E. K. Lee, M. Jung, D. Shin, I. Y. Jeon, S. M. Jung, H. J. Choi, J. M. Seo, S. Y. Bae, S. D. Sohn, N. Park, J. H. Oh, H. J. Shin and J. B. Baek, *Nat. Commun.*, 2015, **6**, 6486.
- 268 R. Walczak, B. Kurpil, A. Savateev, T. Heil, J. Schmidt, Q. Qin, M. Antonietti and M. Oschatz, *Angew. Chem., Int. Ed.*, 2018, **57**, 10765.
- 269 S. Zhang, J. Zhou, Q. Wang and P. Jena, *J. Phys. Chem. C*, 2016, **120**, 3993–3998.
- 270 S. Yang, W. Li, C. Ye, G. Wang, H. Tian, C. Zhu, P. He, G. Ding, X. Xie, Y. Liu and Y. Lifshitz, *Adv. Mater.*, 2017, **29**, 1605625.
- 271 J. Mahmood, E. K. Lee, M. Jung, D. Shin, H. J. Choi, J. M. Seo, S. M. Jung, D. Kim, F. Li, M. S. Lah and N. Park, *Proc. Natl. Acad. Sci. U. S. A.*, 2016, **113**, 7414–7419.
- 272 S. Kim and H. C. Choi, *Commun. Chem.*, 2019, **2**, 60.
- 273 S. Cao, J. Low, J. Yu and M. Jaroniec, *Adv. Mater.*, 2015, **27**, 2150–2176.
- 274 L. Jiang, X. Yuan, Y. Pan, J. Liang, G. Zeng, Z. Wu and H. Wang, *Appl. Catal., B*, 2017, **217**, 388–406.
- 275 Y. Luo, Y. Yan, S. Zheng, H. Xue and H. Pang, *J. Mater. Chem. A*, 2019, **7**, 901–924.
- 276 S. N. Talapaneni, J. H. Lee, S. H. Je, O. Buyukcakir, T. W. Kwon, K. Polychronopoulou, J. W. Choi and A. Coskun, *Adv. Funct. Mater.*, 2017, **27**, 1604658.
- 277 W. Niu and Y. Yang, *ACS Energy Lett.*, 2018, **3**, 2796–2815.
- 278 X. Chen, Q. Liu, Q. Wu, P. Du, J. Zhu, S. Dai and S. Yang, *Adv. Funct. Mater.*, 2016, **26**, 1719–1728.
- 279 J. Xu, T. J. Brenner, L. Chabanne, D. Neher, M. Antonietti and M. Shalom, *J. Am. Chem. Soc.*, 2014, **136**, 13486–13489.
- 280 J. Xu, G. Wang, J. Fan, B. Liu, S. Cao and J. Yu, *J. Power Sources*, 2015, **274**, 77–84.
- 281 I. Mohammadi, F. Zeraatpisheh, E. Ashiri and K. Abdi, *Int. J. Hydrogen Energy*, 2020, **45**, 18831–18839.
- 282 Z. Yuan, R. Tang, Y. Zhang and L. Yin, *J. Alloys Compd.*, 2017, **691**, 983–991.
- 283 J. Chen, H. Dong, L. Zhang, J. Li, F. Jia, B. Jiao, J. Xu, X. Hou, J. Liu and Z. Wu, *J. Mater. Chem. A*, 2020, **8**, 2644–2653.
- 284 D. Cruz, J. Garcia Cerrillo, B. Kumru, N. Li, J. Dario Perea, B. V. Schmidt, I. Lauermann, C. J. Brabec and M. Antonietti, *J. Am. Chem. Soc.*, 2019, **141**, 12322–12328.
- 285 P. Liu, Y. Sun, S. Wang, H. Zhang, Y. Gong, F. Li, Y. Shi, Y. Du, X. Li, S. S. Guo and Q. Tai, *J. Power Sources*, 2020, **451**, 227825.
- 286 L. L. Jiang, Z. K. Wang, M. Li, C. C. Zhang, Q. Q. Ye, K. H. Hu, D. Z. Lu, P. F. Fang and L. S. Liao, *Adv. Funct. Mater.*, 2018, **28**, 1705875.
- 287 H. Peelaers, M. L. Chabinye and C. G. Van de Walle, *Chem. Mater.*, 2017, **29**, 2563–2567.
- 288 J. C. Bernède, S. Houari, D. Nguyen, P. Y. Jouan, A. Khelil, A. Mokrani, L. Cattin and P. Predeep, *Phys. Status Solidi A*, 2012, **209**, 1291–1297.
- 289 Y. Guo and J. Robertson, *Appl. Phys. Lett.*, 2014, **105**, 222110.
- 290 M. H. Li, P. S. Shen, K. C. Wang, T. F. Guo and P. Chen, *J. Mater. Chem. A*, 2015, **3**, 9011–9019.
- 291 M. Kröger, S. Hamwi, J. Meyer, T. Riedl, W. Kowalsky and A. Kahn, *Appl. Phys. Lett.*, 2009, **95**, 123301.
- 292 K. H. Wong, K. Ananthanarayanan, J. Luther and P. Balaya, *J. Phys. Chem. C*, 2012, **116**, 16346.



- 293 M. Kröger, S. Hamwi, J. Meyer, T. Riedl, W. Kowalsky and A. Kahn, *Org. Electron.*, 2009, **10**, 932–938.
- 294 G. Fiori, F. Bonaccorso, G. Iannaccone, T. Palacios, D. Neumaier, A. Seabaugh, S. K. Banerjee and L. Colombo, *Nat. Nanotechnol.*, 2014, **9**, 768.
- 295 F. Schwierz, *Nat. Nanotechnol.*, 2010, **5**, 487.
- 296 F. Bonaccorso, P. H. Tan and A. C. Ferrari, *ACS Nano*, 2013, **7**, 1838.
- 297 C. Backes, *et al.*, *2D Mater.*, 2020, **7**, 022001.
- 298 F. Bonaccorso and Z. Sun, *Opt. Mater. Express*, 2014, **4**, 63.
- 299 K. S. Novoselov, D. Jiang, F. Schedin, T. J. Booth, V. V. Khotkevich, S. V. Morozov and A. K. Geim, *Proc. Natl. Acad. Sci. U. S. A.*, 2005, **102**, 10451.
- 300 X. S. Li, C. W. Magnuson, A. Venugopal, R. M. Tromp, J. B. Hannon, E. M. Vogel, L. Colombo and R. S. Ruoff, *J. Am. Chem. Soc.*, 2011, **133**, 2816.
- 301 Y. F. Hao, M. S. Bharathi, L. Wang, Y. Y. Liu, H. Chen, S. Nie, X. H. Wang, H. Chou, C. Tan, B. Fallahazad, H. Ramanarayan, C. W. Magnuson, E. Tutuc, B. I. Yakobson, K. F. McCarty, Y. W. Zhang, P. Kim, J. Hone, L. Colombo and R. S. Ruoff, *Science*, 2013, **342**, 720.
- 302 J. Jeon, S. K. Jang, S. M. Jeon, G. Yoo, Y. H. Jang, J. H. Park and S. Lee, *Nanoscale*, 2015, **7**, 1688–1695.
- 303 C. Xu, L. Wang, Z. Liu, L. Chen, J. Guo, N. Kang, X. L. Ma, H. M. Cheng and W. Ren, *Nat. Mater.*, 2015, **14**, 1135–1141.
- 304 S. M. Kim, A. Hsu, M. H. Park, S. H. Chae, S. J. Yun, J. S. Lee, D. H. Cho, W. Fang, C. Lee, T. Palacios and M. Dresselhaus, *Nat. Commun.*, 2015, **6**, 8662.
- 305 Y. Chen, X. L. Gong and J. G. Gai, *Adv. Sci.*, 2016, **3**, 1500343.
- 306 L. Di Gaspere, A. M. Scaparro, M. Fanfoni, L. Fazi, A. Sgarlata, A. Notargiacomo, V. Miseikis, C. Coletti and M. De Seta, *Carbon*, 2018, **134**, 183–188.
- 307 B. Deng, Z. Liu and H. Peng, *Adv. Mater.*, 2019, **31**, 1800996.
- 308 A. Shivayogimath, P. R. Whelan, D. M. Mackenzie, B. Luo, D. Huang, D. Luo, M. Wang, L. Gammelgaard, H. Shi, R. S. Ruoff and P. Bøggild, *Chem. Mater.*, 2019, **31**, 2328–2336.
- 309 X. Li, W. Cai, J. An, S. Kim, J. Nah, D. Yang, R. Piner, A. Velamakanni, I. Jung, E. Tutuc and S. BaK nerjee, *Science*, 2009, **324**, 1312–1314.
- 310 K. V. Emtsev, A. Bostwick, K. Horn, J. Jobst, G. L. Kellogg, L. Ley, J. L. McChesney, T. Ohta, S. A. Reshanov, J. Röhl, E. Rotenberg, A. K. Schmid, D. Waldmann, H. B. Weber and T. Seyller, *Nat. Mater.*, 2009, **8**, 203.
- 311 C. Berger, Z. Song, T. Li, X. Li, A. Y. Ogbazghi, R. Feng, Z. Dai, A. N. Marchenkov, E. H. Conrad, P. N. First and W. A. de Heer, *J. Phys. Chem. B*, 2004, **108**, 19912.
- 312 Y. Zhang, Y. Yao, M. G. Sendeku, L. Yin, X. Zhan, F. Wang, Z. Wang and J. He, *Adv. Mater.*, 2019, **31**, 1901694.
- 313 J. Cheng, C. Wang, X. Zou and L. Liao, *Adv. Opt. Mater.*, 2019, **7**, 1800441.
- 314 Y. I. Zhang, L. Zhang and C. Zhou, *Acc. Chem. Res.*, 2013, **46**, 2329–2339.
- 315 W. S. Leong, H. Wang, J. Yeo, F. J. Martin-Martinez, A. Zubair, P. C. Shen, Y. Mao, T. Palacios, M. J. Buehler, J. Y. Hong and J. Kong, *Nat. Commun.*, 2019, **10**, 1–8.
- 316 Y. Kim, S. S. Cruz, K. Lee, B. O. Alawode, C. Choi, Y. Song, J. M. Johnson, C. Heidelberger, W. Kong, S. Choi and K. Qiao, *Nature*, 2017, **544**, 340–343.
- 317 D. De Fazio, D. G. Purdie, A. K. Ott, P. Braeuninger-Weimer, T. Khodkov, S. Goossens, T. Taniguchi, K. Watanabe, P. Livreri, F. H. Koppens and F. S. Hofmann, *ACS Nano*, 2019, **13**, 8926–8935.
- 318 B. N. Chandrashekar, A. S. Smitha, Y. Wu, N. Cai, Y. Li, Z. Huang, W. Wang, R. Shi, J. Wang, S. Liu and S. Krishnaveni, *Sci. Rep.*, 2019, **9**, 1–11.
- 319 L. P. Ma, W. Ren and H. M. Cheng, *Small Methods*, 2019, **3**, 1900049.
- 320 J. W. Suk, A. Kitt, C. W. Magnuson, Y. Hao, S. Ahmed, J. An, A. K. Swan, B. B. Goldberg and R. S. Ruoff, *ACS Nano*, 2011, **5**, 6916–6924.
- 321 J. Kang, D. Shin, S. Bae and B. H. Hong, *Nanoscale*, 2012, **4**, 5527–5537.
- 322 A. Castellanos-Gomez, M. Buscema, R. Molenaar, V. Singh, L. Janssen, H. S. Van der Zant and G. A. Steele, *2D Mater.*, 2014, **1**, 011002.
- 323 L. Banszerus, M. Schmitz, S. Engels, J. Dauber, M. Oellers, F. Haupt, K. Watanabe, T. Taniguchi, B. Beschoten and C. Stampfer, *Sci. Adv.*, 2015, **1**, e1500222.
- 324 Z. Chen, Y. Qi, X. Chen, Y. Zhang and Z. Liu, *Adv. Mater.*, 2019, **31**, 1803639.
- 325 J. Sun, Y. Chen, M. K. Priyadarshi, T. Gao, X. Song, Y. Zhang and Z. Liu, *Adv. Mater.*, 2016, **28**, 10333.
- 326 J. Sun, Y. Chen, M. K. Priyadarshi, Z. Chen, A. Bachmatiuk, Z. Zou, Z. Chen, X. Song, Y. Gao, M. H. Ruemmeli, Y. Zhang and Z. Liu, *Nano Lett.*, 2015, **15**, 5846.
- 327 Y. Chen, J. Sun, J. Gao, F. Du, Q. Han, Y. Nie, Z. Chen, A. Bachmatiuk, M. K. Priyadarshi, D. Ma, X. Song, X. Wu, C. Xiong, M. H. Ruemmeli, F. Ding, Y. Zhang and Z. Liu, *Adv. Mater.*, 2015, **27**, 7839.
- 328 Y. Hernandez, V. Nicolosi, M. Lotya, F. M. Blighe, Z. Sun, S. De, I. T. McGovern, B. Holland, M. Byrne, Y. K. Gun'Ko, J. J. Boland, P. Niraj, G. Duesberg, S. Krishnamurthy, R. Goodhue, J. Hutchison, V. Scardaci, A. C. Ferrari and J. N. Coleman, *Nat. Nanotechnol.*, 2008, **3**, 563.
- 329 T. Hasan, F. Torrisi, Z. Sun, D. Popa, V. Nicolosi, G. Privitera, F. Bonaccorso and A. C. Ferrari, *Phys. Status Solidi B*, 2010, **247**, 2953.
- 330 J. N. Coleman, M. Lotya, A. O'Neill, S. D. Bergin, P. J. King, U. Khan, K. Young, A. Gaucher, S. De, R. J. Smith, I. V. Shvets, S. K. Arora, G. Stanton, H. Y. Kim, K. Lee, G. T. Kim, G. S. Duesberg, T. Hallam, J. J. Boland, J. J. Wang, J. F. Donegan, J. C. Grunlan, G. Moriarty, A. Shmeliov, R. J. Nicholls, J. M. Perkins, E. M. Grievson, K. Theuwissen, D. W. McComb, P. D. Nellist and V. Nicolosi, *Science*, 2011, **331**, 568.
- 331 J. N. Coleman, *Adv. Funct. Mater.*, 2009, **19**, 3680–3695.
- 332 F. Torrisi, T. Hasan, W. P. Wu, Z. P. Sun, A. Lombardo, T. S. Kulmala, G. W. Hsieh, S. J. Jung, F. Bonaccorso,



- P. J. Paul, D. P. Chu and A. C. Ferrari, *ACS Nano*, 2012, **6**, 2992.
- 333 A. Capasso, A. E. D. Castillo, H. Sun, A. Ansaldò, V. Pellegrini and F. Bonaccorso, *Solid State Commun.*, 2015, **224**, 53–63.
- 334 A. E. Del Rio Castillo, V. Pellegrini, H. Sun, J. Buha, D. A. Dinh, E. Lago, A. Ansaldò, A. Capasso, L. Manna and F. Bonaccorso, *Chem. Mater.*, 2018, **30**, 506.
- 335 S. Essig, C. W. Marquardt, A. Vijayaraghavan, M. Ganzhorn, S. Dehm, F. Hennrich, F. Ou, A. A. Green, C. Sciascia, F. Bonaccorso, K.-P. Bohnen, H. V. Lohneysen, M. M. Kappes, P. M. Ajayan, M. C. Hersam, A. C. Ferrari and R. Krupke, *Nano Lett.*, 2010, **10**, 1589.
- 336 H. Zhu, Y. Cao, J. Zhang, W. Zhang, Y. Xu, J. Guo, W. Yang and J. Liu, *J. Mater. Sci.*, 2016, **51**, 3675–3683.
- 337 G. Kakavelakis, A. E. Del Rio Castillo, V. Pellegrini, A. Ansaldò, P. Tzourmpakis, P. Brescia, M. Prato, E. Stratakis, E. Kymakis and F. Bonaccorso, *ACS Nano*, 2017, **11**, 3517–3531.
- 338 O. M. Marago, F. Bonaccorso, R. Saija, G. Privitera, P. G. Gucciardi, M. A. Iati, G. Calogero, P. H. Jones, F. Borghese, P. Denti, V. Nicolosi and A. C. Ferrari, *ACS Nano*, 2010, **4**, 7515.
- 339 M. Lotya, Y. Hernandez, P. J. King, R. J. Smith, V. Nicolosi, L. S. Karlsson, F. M. Blighe, S. De, Z. Wang, I. T. McGovern, G. S. Duesberg and J. N. Coleman, *J. Am. Chem. Soc.*, 2009, **131**, 3611.
- 340 A. A. Green and M. C. Hersam, *Nano Lett.*, 2009, **9**, 4031.
- 341 P. May, U. Khan, J. M. Hughes and J. N. Coleman, *J. Phys. Chem. C*, 2012, **116**, 11393.
- 342 G. Guan, S. Zhang, S. Liu, Y. Cai, M. Low, C. P. Teng, I. Y. Phang, Y. Cheng, K. L. Duei, B. M. Srinivasan, Y. Zheng, Y.-W. Zhang and M.-Y. Han, *J. Am. Chem. Soc.*, 2015, **137**, 6152.
- 343 S. M. Notley, *Langmuir*, 2012, **28**, 14110.
- 344 M. Yi and Z. Shen, *J. Mater. Chem. A*, 2015, **3**, 11700–11715.
- 345 A. Ciesielski and P. Samorì, *Chem. Soc. Rev.*, 2014, **43**, 381.
- 346 M. Lotya, P. J. King, U. Khan, S. De and J. N. Coleman, *ACS Nano*, 2010, **4**, 3155.
- 347 C. E. Hamilton, J. R. Lomeda, Z. Sun, J. M. Tour and A. R. Barron, *Nano Lett.*, 2009, **9**, 3460.
- 348 C. J. Shih, A. Vijayaraghavan, R. Krishnan, R. Sharma, J.-H. Han, M.-H. Ham, Z. Jin, S. Lin, G. L. C. Paulus, N. F. Reuel and Q. H. Wang, *Nat. Nanotechnol.*, 2011, **6**, 439.
- 349 A. Ciesielski, S. Haar, A. Aliprandi, M. El Garah, G. Tregnago, G. F. Cotella, M. El Gemayel, F. Richard, H. Sun, F. Cacialli, F. Bonaccorso and P. Samorì, *ACS Nano*, 2016, **10**, 10768–10777.
- 350 U. Khan, A. O'Neill, M. Lotya, S. De and J. N. Coleman, *Small*, 2010, **6**, 864.
- 351 W. Zhao, M. Fang, F. Wu, H. Wu, L. Wang and G. Chen, *J. Mater. Chem.*, 2010, **20**, 5817.
- 352 A. E. Del Rio-Castillo, C. Merino, E. Díez-Barra and E. Vázquez, *Nano Res.*, 2014, **7**, 963.
- 353 C. Damm, T. J. Nacken and W. Peukert, *Carbon*, 2015, **81**, 284.
- 354 K. R. Paton, E. Varrla, C. Backes, R. J. Smith, U. Khan, A. O'Neill, C. Boland, M. Lotya, O. M. Istrate, P. King, T. Higgins, S. Barwich, P. May, P. Puczkarski, I. Ahmed, M. Moebius, H. Pettersson, E. Long, J. Coelho, S. E. O'Brien, E. K. McGuire, B. M. Sanchez, G. S. Duesberg, N. McEvoy, T. J. Pennycook, C. Downing, A. Crossley, V. Nicolosi and J. N. Coleman, *Nat. Mater.*, 2014, **13**, 624.
- 355 E. Varrla, K. R. Paton, C. Backes, A. Harvey, R. J. Smith, J. McCauley and J. N. Coleman, *Nanoscale*, 2014, **6**, 11810.
- 356 H. Yurdakul, Y. Göncü, O. Durukan, A. Akay, A. T. Seyhan, N. Ay and S. Turan, *Ceram. Int.*, 2012, **38**, 2187.
- 357 A. T. Seyhan, Y. Göncü, O. Durukan, A. Akay and N. Ay, *J. Solid State Chem.*, 2017, **249**, 98.
- 358 M. Buzaglo, M. Shtein and O. Regev, *Chem. Mater.*, 2016, **28**, 21.
- 359 P. G. Karagiannidis, S. A. Hodge, L. Lombardi, F. Tomarchio, N. Decorde, S. Milana, I. Goykhman, Y. Su, S. V. Mesite, D. N. Johnstone, R. K. Leary, P. A. Midgley, N. M. Pugno, F. Torrisi and A. C. Ferrari, *ACS Nano*, 2017, **11**, 2742.
- 360 A. E. Del Rio Castillo, V. Pellegrini, A. Ansaldò, F. Ricciardella, H. Sun, L. Marasco, J. Buha, Z. Dang, L. Gagliani, E. Lago, N. Curreli, S. Gentiluomo, F. Palazon, M. Prato, R. Oropesa-Nuñez, P. S. Toth, E. Mantero, M. Crugliano, A. Gamucci, A. Tomadin, M. Polini and F. Bonaccorso, *Mater. Horiz.*, 2018, **5**, 890.
- 361 A. E. Del Rio Castillo, A. Ansaldò, V. Pellegrini and F. Bonaccorso, *Exfoliation materials by wet-jet milling techniques*, WO2017/089987A1, 2016.
- 362 S. Bellani, L. Najafi, M. Prato, R. Oropesa-Nuñez, B. Martín-García, L. Gagliani, E. Mantero, L. Marasco, G. Bianca, M. I. Zappia, C. Demirci, S. Olivotto, G. Mariucci, V. Pellegrini, M. Schiavetti and F. Bonaccorso, *Chem. Mater.*, 2021, **33**, 4106.
- 363 S. Bellani, E. Petroni, A. E. Del Rio Castillo, N. Curreli, B. Martín-García, R. Oropesa-Nuñez, M. Prato and F. Bonaccorso, *Adv. Funct. Mater.*, 2019, **29**, 1807659.
- 364 V. Romano, B. Martín-García, S. Bellani, L. Marasco, J.-K. Panda, R. Oropesa-Nuñez, L. Najafi, A. E. Del Rio Castillo, M. Prato, E. Mantero and V. Pellegrini, *Chem-PlusChem*, 2019, **84**, 882.
- 365 S. Bellani, F. Wang, G. Longoni, L. Najafi, R. Oropesa-Nuñez, A. E. Del Rio Castillo, M. Prato, X. Zhuang, V. Pellegrini, X. Feng and X. F. Bonaccorso, *Nano Lett.*, 2018, **18**, 7155.
- 366 S. Bellani, B. Martín-García, R. Oropesa-Nuñez, V. Romano, L. Najafi, C. Demirci, M. Prato, A. E. Del Rio Castillo, L. Marasco, E. Mantero, G. D'Angelo and F. Bonaccorso, *Nanoscale Horiz.*, 2019, **4**, 1077.
- 367 S. Palumbo, L. Silvestri, A. Ansaldò, R. Brescia, F. Bonaccorso and V. Pellegrini, *ACS Appl. Energy Mater.*, 2019, **2**, 1793.
- 368 L. Carbone, A. E. Del Rio Castillo, J.-K. Panda, G. Pugliese, A. Scarpellini, F. Bonaccorso and V. Pellegrini, *ChemSusChem*, 2020, **13**, 1593–1602.
- 369 S. Bellani, L. Najafi, M. Prato, R. Oropesa-Nuñez, B. Martín-García, L. Gagliani, E. Mantero, L. Marasco, G. Bianca, M. I. Zappia, C. Demirci, S. Olivotto,



- G. Mariucci, V. Pellegrini, M. Schiavetti and F. Bonaccorso, *Chem. Mater.*, 2021, **33**(11), 4106–4121.
- 370 E. Greco, G. Nava, R. Fathi, F. Fumagalli, A. E. Del Rio-Castillo, A. Ansaldo, S. Monaco, F. Bonaccorso, V. Pellegrini and F. Di Fonzo, *J. Mater. Chem. A*, 2017, **5**, 19306.
- 371 S. Palumbo, L. Silvestri, A. Ansaldo, R. Brescia, F. Bonaccorso and V. Pellegrini, *ACS Appl. Energy Mater.*, 2019, **2**, 1793.
- 372 A. E. Del Rio Castillo, C. D. Reyes-Vazquez, L. E. Rojas-Martinez, S. B. Thorat, M. Serri, A. L. Martinez-Hernandez, C. Velasco-Santos, V. Pellegrini and F. Bonaccorso, *FlatChem*, 2019, **18**, 100131.
- 373 A. M. Abdelkader, A. J. Cooper, R. A. W. Dryfe and I. A. Kinloch, *Nanoscale*, 2015, **7**, 6944.
- 374 P. Yu, S. E. Lowe, G. P. Simon and Y. L. Zhong, *Curr. Opin. Colloid Interface Sci.*, 2015, **20**, 329.
- 375 S. Yang, M. R. Lohe, K. Müllen and X. Feng, *Adv. Mater.*, 2016, **28**, 6213.
- 376 F. Bonaccorso, T. Hasan, P. H. Tan, C. Sciascia, G. Privitera, G. Di Marco, P. G. Gucciardi and A. C. Ferrari, *J. Phys. Chem. C*, 2010, **114**, 17267.
- 377 T. Hasan, P. H. Tan, F. Bonaccorso, A. G. Rozhin, V. Scardaci, W. I. Milne and A. C. Ferrari, *J. Phys. Chem. C*, 2008, **112**, 20227.
- 378 T. Hasan, Z. Sun, P. H. Tan, D. Popa, E. Flahaut, E. J. R. Kelleher, F. Bonaccorso, F. Wang, Z. Jiang, F. Torrisi, G. Privitera, V. Nicolosi and A. C. Ferrari, *ACS Nano*, 2014, **8**, 4836.
- 379 F. Schoppler, C. Mann, T. C. Hain, F. M. Neubauer, G. Privitera, F. Bonaccorso, D. Chu, A. C. Ferrari and T. Hertel, *J. Phys. Chem. C*, 2011, **115**, 14682.
- 380 O. M. Maragò, P. H. Jones, F. Bonaccorso, V. Scardaci, P. G. Gucciardi, A. G. Rozhin and A. C. Ferrari, *Nano Lett.*, 2008, **8**, 3211.
- 381 M. G. Donato, S. Vasi, R. Sayed, P. H. Jones, F. Bonaccorso, A. C. Ferrari, P. G. Gucciardi and O. M. Maragò, *Opt. Lett.*, 2012, **37**, 3381.
- 382 T. Svedberg, K. O. Pedersen and J. H. Bauer, *The ultra-centrifuge*, Clarendon Press, Oxford, 1940.
- 383 D. A. Brownson, J. P. Metters, D. K. Kampouris and C. E. Banks, *Electroanalysis*, 2011, **23**, 894–899.
- 384 C. J. Shih, G. L. Paulus, Q. H. Wang, Z. Jin, D. Blankschtein and D. M. S. Strano, *Langmuir*, 2012, **28**, 8579–8586.
- 385 J. O. Island, G. A. Steele, H. S. van der Zant and A. Castellanos-Gomez, *2D Mater.*, 2015, **2**, 011002.
- 386 A. A. Kistanov, Y. Cai, K. Zhou, S. V. Dmitriev and Y. W. Zhang, *2D Mater.*, 2016, **4**, 015010.
- 387 X. Li, W. Cai, J. An, S. Kim, J. Nah, D. Yang, R. Piner, A. Velamakanni, I. Jung, E. Tutuc, S. K. Banerjee, L. Colombo and R. S. Ruoff, *Science*, 2009, **324**, 1312.
- 388 S. Bae, H. Kim, Y. Lee, X. Xu, J.-S. Park, Y. Zheng, J. Balakrishnan, T. Lei, H. Ri Kim, Y. I. Song, Y.-J. Kim, K. S. Kim, B. Özyilmaz, J.-H. Ahn, B. H. Hong and S. Iijima, *Nat. Nanotechnol.*, 2010, **5**, 574.
- 389 R. F. Frindt, *J. Phys. Chem. Solids*, 1963, **24**, 1107.
- 390 X. K. Lu, M. F. Yu, H. Huang and R. S. Ruoff, *Nanotechnology*, 1999, **10**, 269.
- 391 D. A. Dikin, S. Stankovich, E. J. Zimney, R. D. Piner, G. H. B. Dommett, G. Evmenenko, S. T. Nguyen and R. S. Ruoff, *Nature*, 2007, **448**, 457.
- 392 H. C. Schniepp, J. L. Li, M. J. McAllister, H. Sai, M. Herrera-Alonso, D. H. Adamson, R. K. Prud'homme, R. Car, D. A. Saville and I. A. Aksay, *J. Phys. Chem. B*, 2006, **110**, 8535.
- 393 S. Stankovich, D. A. Dikin, R. D. Piner, K. A. Kohlhaas, A. Kleinhammes, Y. Jia, Y. Wu, S. T. Nguyen and R. S. Ruoff, *Carbon*, 2007, **45**, 1558.
- 394 J. R. Lomeda, C. D. Doyle, D. V. Kosynkin, W. F. Hwang and J. M. Tour, *J. Am. Chem. Soc.*, 2008, **130**, 16201.
- 395 B. Konkana and S. Vasudevan, *J. Phys. Chem. Lett.*, 2012, **3**, 867–872.
- 396 J. Kim, L. J. Cote, F. Kim, W. Yuan, K. R. Shull and J. Huang, *J. Am. Chem. Soc.*, 2010, **132**, 8180–8186.
- 397 G. Wang, X. Shen, B. Wang, J. Yao and J. Park, *Carbon*, 2009, **47**, 1359–1364.
- 398 X. Li, X. Wang, L. Zhang, S. Lee and H. Dai, *Science*, 2008, **319**, 1229.
- 399 C.-Y. Su, Y. Xu, W. Zhang, J. Zhao, X. Tang, C.-H. Tsai and L.-J. Li, *Chem. Mater.*, 2009, **21**, 5674.
- 400 H. L. Wang, J. T. Robinson, X. L. Li and H. J. Dai, *J. Am. Chem. Soc.*, 2009, **131**, 9910.
- 401 D. Voiry, J. Yang, J. Kupferberg, R. Fullon, C. Lee, H. Y. Jeong, H. S. Shin and M. Chhowalla, *Science*, 2016, **353**, 1413.
- 402 H. Kim, C. Mattevi, H. J. Kim, A. Mittal, K. A. Mkhoyan, R. E. Riman and M. Chhowalla, *Nanoscale*, 2013, **5**, 12365–12374.
- 403 V. C. Tung, M. J. Allen, Y. Yang and R. B. Kaner, *Nat. Nanotechnol.*, 2009, **4**, 25.
- 404 Y. Xu, G. Long, L. Huang, Y. Huang, X. Wan, Y. Ma and Y. Chen, *Carbon*, 2010, **48**, 3308–3311.
- 405 S. Bellani, M. R. Antognazza and F. Bonaccorso, *Adv. Mater.*, 2019, **31**, 1801446.
- 406 S. Casaluci, M. Gemmi, V. Pellegrini, A. Di Carlo and F. Bonaccorso, *Nanoscale*, 2016, **8**, 5368–5378.
- 407 A. Capasso, S. Bellani, A. L. Palma, L. Najafi, A. E. Del Rio Castillo, N. Curreli, L. Cinà, V. Miseikis, C. Coletti, G. Calogero, V. Pellegrini, A. Di Carlo and F. Bonaccorso, *2D Mater.*, 2019, **6**, 035007.
- 408 A. Ansaldo, P. Bondavalli, S. Bellani, A. E. Del Rio Castillo, M. Prato, V. Pellegrini, G. Pognon and F. Bonaccorso, *ChemNanoMat*, 2017, **3**, 436.
- 409 L. Najafi, S. Bellani, R. Oropesa-Nuñez, B. Martín-García, M. Prato and F. Bonaccorso, *ACS Appl. Energy Mater.*, 2019, **2**, 5373.
- 410 L. Najafi, S. Bellani, R. Oropesa-Nuñez, M. Prato, B. Martín-García, R. Brescia and F. Bonaccorso, *ACS Nano*, 2019, **13**, 3162.
- 411 L. Najafi, S. Bellani, R. Oropesa-Nuñez, A. Ansaldo, M. Prato, A. E. Del Rio Castillo and F. Bonaccorso, *Adv. Energy Mater.*, 2018, **25**, 1801764.
- 412 E. Petroni, E. Lago, S. Bellani, D. W. Boukhvalov, A. Politano, B. Gürbulak, S. Duman, M. Prato, S. Gentiluomo, R. Oropesa-



- Núñez, J.-K. Panda, P. S. Toth, A. E. Del Rio Castillo, V. Pellegrini and F. Bonaccorso, *Small*, 2018, **14**, 1800749.
- 413 L. Najafi, S. Bellani, R. Oropesa-Núñez, A. Ansaldo, M. Prato, A. E. Del Rio Castillo and F. Bonaccorso, *Adv. Energy Mater.*, 2018, **8**, 1703212.
- 414 L. Najafi, S. Bellani, B. Martín-García, R. Oropesa-Núñez, A. E. Del Rio Castillo, M. Prato, I. Moreels and F. Bonaccorso, *Chem. Mater.*, 2017, **29**, 5782.
- 415 L. Najafi, S. Bellani, A. Castelli, M. P. Arciniegas, R. Brescia, R. Oropesa-Núñez, B. Martín-García, M. Serri, F. Drago, L. Manna and F. Bonaccorso, *Chem. Mater.*, 2020, **32**, 2420–2429.
- 416 S. K. Karunakaran, G. M. Arumugam, W. Yang, S. Ge, S. N. Khan, X. Lin and G. Yang, *J. Mater. Chem. A*, 2019, **7**, 13873–13902.
- 417 M. M. Voigt, R. C. Mackenzie, S. P. King, C. P. Yau, P. Atienzar, J. Dane, P. E. Keivanidis, I. Zadrzil, D. D. Bradley and J. Nelson, *Sol. Energy Mater. Sol. Cells*, 2012, **105**, 77–85.
- 418 S. Alem, N. Graddage, J. Lu, T. Kololuoma, R. Movileanu and Y. Tao, *Org. Electron.*, 2018, **52**, 146–152.
- 419 K. Cao, Z. Zuo, J. Cui, Y. Shen, T. Moehl, S. M. Zakeeruddin, M. Grätzel and M. Wang, *Nano Energy*, 2015, **17**, 171–179.
- 420 F. C. Krebs, J. Fyenbo and M. Jørgensen, *J. Mater. Chem.*, 2010, **20**, 8994–9001.
- 421 A. G. Kelly, T. Hallam, C. Backes, A. Harvey, A. S. Esmaily, I. Godwin, J. Coelho, V. Nicolosi, J. Lauth, A. Kulkarni, S. Kinge, L. D. A. Siebbeles, G. S. Duesberg and J. N. Coleman, *Science*, 2017, **356**, 69.
- 422 A. Hirsch and F. Hauke, *Angew. Chem., Int. Ed.*, 2018, **57**, 4338.
- 423 D. Chen, H. Feng and J. Li, *Chem. Rev.*, 2012, **112**, 6027.
- 424 A. Hirsch, J. M. Englert and F. Hauke, *Acc. Chem. Res.*, 2012, **46**, 87.
- 425 L. Najafi, R. Oropesa-Núñez, B. Martín-García, F. Drago, M. Prato, V. Pellegrini, F. Bonaccorso and S. Bellani, *Mater. Adv.*, 2020, **1**, 387–402.
- 426 G. Haacke, *J. Appl. Phys.*, 1976, **47**, 4086–4089.
- 427 K. Seeger, *“Semiconductor Physics: An introduction”*, Springer-Verlag, Berlin Heidelberg, 9th ed., 2004.
- 428 M. Dressel and G. Gruner, *Electrodynamics of solids*, Cambridge University Press, UK, 2002, ch. 8.
- 429 L. Hu, D. S. Hecht and G. Gruner, *Nano Lett.*, 2004, **4**, 2513–2517.
- 430 R. E. Glover and M. Tinkham, *Phys. Rev.*, 1957, **108**, 243–256.
- 431 T. M. Barnes, M. O. Reese, J. D. Bergeson, B. A. Larsen, J. L. Blackburn, M. C. Beard, J. Bult and J. van de Lagemaat, *Adv. Energy Mater.*, 2012, **2**, 353–360.
- 432 K. Ellmer, *Nat. Photonics*, 2012, **6**, 809–817.
- 433 P. Drude, *Ann. Phys.*, 1900, **308**, 369–402.
- 434 A. Hauch and A. Georg, *Electrochim. Acta*, 2001, **46**, 3457–3466.
- 435 F. Fabregat-Santiago, J. Bisquert, E. Palomares, L. Otero, D. Kuang, S. Zakeeruddin and M. Grätzel, *J. Phys. Chem. C*, 2007, **111**, 6550–6560.
- 436 B. Zhang, D. Wang, Y. Hou, S. Yang, X. Yang, J. Zhong, J. Liu, H. Wang, P. Hu, H. Zhao and H. Yang, *Sci. Rep.*, 2013, **3**, 1836–1843.
- 437 N. Koide, A. Islam, Y. Chiba and L. Han, *J. Photochem. Photobiol., A*, 2006, **182**, 296–305.
- 438 D. Pysch, A. Mette and S. Glunz, *Sol. Energy Mater. Sol. Cells*, 2007, **91**, 1698–1706.
- 439 X. Yin, Z. Xue and B. Liu, *J. Power Sources*, 2011, **196**, 2422–2426.
- 440 C. Chen, C. Chen and T. Wei, *Electrochim. Acta*, 2010, **55**, 1687–1695.
- 441 S. Park, H. Boo and T. Chung, *Anal. Chim. Acta*, 2006, **556**, 46–57.
- 442 T. N. Murakami and M. Grätzel, *Inorg. Chim. Acta*, 2008, **361**, 572–580.
- 443 G. Yu, J. Gao, J. Hummelen, F. Wudl and A. Heeger, *Science*, 1995, **270**, 1789–1790.
- 444 J. S. Wu, S. W. Cheng, Y. J. Cheng and C. S. Hsu, *Chem. Soc. Rev.*, 2015, **44**, 1113–1154.
- 445 L. Lu, T. Zheng, Q. Wu, A. M. Schneider, D. Zhao and L. Yu, *Chem. Rev.*, 2015, **115**, 12666–12731.
- 446 N. Espinosa, M. Hösel, D. Angmo and F. C. Krebs, *Energy Environ. Sci.*, 2012, **5**, 5117–5132.
- 447 N. S. Sariciftci, L. Smilowitz, A. J. Heeger and F. Wudl, *Science*, 1992, **258**, 1474–1476.
- 448 H. C. Rojas, S. Bellani, E. A. Sarduy, F. Fumagalli, M. T. Mayer, M. Schreier, G. Grätzel, F. Di Fonzo and M. R. Antognazza, *ACS Omega*, 2017, **2**, 3424–3431.
- 449 S. Bellani, L. Najafi, G. Tullii, A. Ansaldo, R. Oropesa-Núñez, M. Prato, M. Colombo, M. R. Antognazza and F. Bonaccorso, *J. Mater. Chem. A*, 2017, **5**, 25177–25186.
- 450 L. Steier, S. Bellani, H. C. Rojas, L. Pan, M. Laitinen, T. Sajavaara, F. Di Fonzo, M. Grätzel, M. R. Antognazza and M. T. Mayer, *Sustainable Energy Fuels*, 2017, **1**, 1915–1920.
- 451 H. C. Rojas, S. Bellani, F. Fumagalli, G. Tullii, S. Leonardi, M. T. Mayer, M. Schreier, M. Grätzel, G. Lanzani, F. Di Fonzo and M. R. Antognazza, *Energy Environ. Sci.*, 2016, **9**, 3710–3723.
- 452 F. Fumagalli, S. Bellani, M. Schreier, S. Leonardi, H. C. Rojas, A. Ghadirzadeh, G. Tullii, A. Savoini, G. Marra, L. Meda and L. M. Grätzel, *J. Mater. Chem. A*, 2016, **4**, 2178–2187.
- 453 A. Guerrero, M. Haro, S. Bellani, M. R. Antognazza, L. Meda, S. Gimenez and J. Bisquert, *Energy Environ. Sci.*, 2014, **7**, 3666–3673.
- 454 A. Ghadirzadeh, F. Fumagalli, A. Mezzetti, S. Bellani, L. Meda, M. R. Antognazza and F. Di Fonzo, *ChemPhotoChem*, 2018, **2**, 283–292.
- 455 L. Najafi, V. Romano, R. Oropesa-Núñez, M. Prato, S. Lauciello, G. D'Angelo, S. Bellani and F. Bonaccorso, *Small Struct.*, 2021, **2**, 2000098.
- 456 G. Li, R. Zhu and Y. Yang, *Nat. Photonics*, 2012, **6**, 153–161.
- 457 J. Kniepert, M. Schubert, J. C. Blakesley and D. J. Neher, *J. Phys. Chem. C*, 2011, **2**, 700–705.



- 458 C.-Z. Li, C.-Y. Chang, Y. Zang, H.-X. Ju, C.-C. Chueh, P.-W. Liang, N. Cho, D. S. Ginger and A. K. Y. Jen, *Adv. Mater.*, 2014, **26**, 6262.
- 459 S. Bellani, A. Iacchetti, M. Porro, L. Beverina, M. R. Antognazza and D. Natali, *Org. Electron.*, 2015, **22**, 56–61.
- 460 D. Ghezzi, M. R. Antognazza, R. Maccarone, S. Bellani, E. Lanzarini, N. Martino, M. Mete, G. Pertile, S. Bisti, G. Lanzani and F. Benfenati, *Nat. Photonics*, 2013, **7**, 400–406.
- 461 S. Bellani, A. Ghadirzadeh, L. Meda, A. Savoini, A. Tacca, G. Marra, R. Meira, J. Morgado, F. Di Fonzo and M. R. Antognazza, *Adv. Funct. Mater.*, 2015, **25**, 4531–4538.
- 462 R. M. Girón, J. Marco-Martínez, S. Bellani, A. Insuasty, H. C. Rojas, G. Tullii, M. R. Antognazza, S. Filippone and N. Martín, *J. Mater. Chem. A*, 2016, **4**, 14284–14290.
- 463 J.-D. Chen, C. Cui, Y.-Q. Li, L. Zhou, Q.-D. Ou, C. Li, Y. Li and J.-X. Tang, *Adv. Mater.*, 2015, **27**, 1035–1041.
- 464 L. Ye, S. Zhang, W. Zhao, H. Yao and J. Hou, *Chem. Mater.*, 2014, **26**, 3603–3605.
- 465 J.-H. Kim, J. B. Park, I. H. Jung, A. C. Grimsdale, S. C. Yoon, H. Yang and D.-H. Hwang, *Energy Environ. Sci.*, 2015, **8**, 2352.
- 466 T. L. Nguyen, H. Choi, S. J. Ko, M. A. Uddin, B. Walker, S. Yum, J. E. Jeong, M. H. Yun, T. J. Shin, S. Hwang, J. Y. Kim and H. Y. Woo, *Energy Environ. Sci.*, 2014, **7**, 3040–3051.
- 467 Z. C. He, B. Xiao, F. Liu, H. B. Wu, Y. L. Yang, S. Xiao, C. Wang, T. P. Russell and Y. Cao, *Nat. Photonics*, 2015, **9**, 174–179.
- 468 J. B. You, L. T. Dou, K. Yoshimura, T. Kato, K. Ohya, T. Moriarty, K. Emery, C. C. Chen, J. Gao, G. Li and Y. Yang, *Nat. Commun.*, 2013, **4**, 1446–1455.
- 469 J. Zhang, H. S. Tan, X. Guo, A. Facchetti and H. Yan, *Nat. Energy*, 2018, **3**, 720–731.
- 470 H. Zhang, H. Yao, J. Hou, J. Zhu, J. Zhang, W. Li, R. Yu, B. Gao, S. Zhang and J. Hou, *Adv. Mater.*, 2018, **30**, 1800613.
- 471 Y. Cui, H. Yao, L. Hong, T. Zhang, Y. Xu, K. Xian, B. Gao, J. Qin, J. Zhang, Z. Wei and J. Hou, *Adv. Mater.*, 2019, **31**, 1808356.
- 472 J. Yuan, Y. Zhang, L. Zhou, G. Zhang, H.-L. Yip, T.-K. Lau, X. Lu, C. Zhu, H. Peng, P. A. Johnson, M. Leclerc, Y. Cao, J. Ulanski, Y. Li and Y. Zou, *Joule*, 2019, **3**, 1140.
- 473 Y. Cui, H. Yao, J. Zhang, T. Zhang, Y. Wang, L. Hong, K. Xian, B. Xu, S. Zhang, J. Peng, Z. Wei, F. Gao and J. Hou, *Nat. Commun.*, 2019, **10**, 2515.
- 474 L. Meng, Y. Zhang, X. Wan, C. Li, X. Zhang, Y. Wang, X. Ke, Z. Xiao, L. Ding, R. Xia, H.-L. Yip, Y. Cao and Y. Chen, *Science*, 2018, **361**, 1904.
- 475 S. Li, C. Z. Li, M. Shi and H. Chen, *ACS Energy Lett.*, 2020, **5**, 1554–1567.
- 476 K. Jiang, Q. Wei, J. Y. L. Lai, Z. Peng, H. K. Kim, J. Yuan, L. Ye, H. Ade, Y. Zou and H. Yan, *Joule*, 2019, **3**, 3020–3033.
- 477 Y. Cui, H. Yao, L. Hong, T. Zhang, Y. Tang, B. Lin, K. Xian, B. Gao, C. An, P. Bi and W. Ma, *Natl. Sci. Rev.*, 2020, **7**, 1239–1246.
- 478 Q. Liu, Y. Jiang, K. Jin, J. Qin, J. Xu, W. Li, J. Xiong, J. Liu, Z. Xiao, K. Sun and S. Yang, *Sci. Bull.*, 2020, **65**, 272–275.
- 479 X. Wang, L. Zhi, N. Tsao, Z. Tomović, J. Li and K. Müllen, *Angew. Chem., Int. Ed.*, 2008, **47**, 2990–2992.
- 480 J. Wu, H. A. Becerril, Z. Bao, Z. Liu, Y. Chen and P. Peumans, *Appl. Phys. Lett.*, 2008, **92**, 237.
- 481 L. Gomez De Arco, Y. Zhang, C. W. Schlenker, K. Ryu, M. E. Thompson and C. Zhou, *ACS Nano*, 2010, **4**, 2865–2873.
- 482 Y. Y. Lee, K. H. Tu, C. C. Yu, S. S. Li, J. Y. Hwang, C. C. Lin, K. H. Chen, L. C. Chen, H. L. Chen and C. W. Chen, *ACS Nano*, 2011, **5**, 6564–6570.
- 483 S. Lee, J. S. Yeo, Y. Ji, C. Cho, D. Y. Kim, S. I. Na, B. H. Lee and T. Lee, *Nanotechnology*, 2012, **23**, 344013.
- 484 Z. Liu, J. Li, Z. H. Sun, G. Tai, S. P. Lau and F. Yan, *ACS Nano*, 2011, **6**, 810–818.
- 485 F. Bonaccorso, N. Balis, M. M. Stylianakis, M. Savarese, C. Adamo, M. Gemmi, V. Pellegrini, E. Stratakis and E. Kymakis, *Adv. Funct. Mater.*, 2015, **25**, 3870–3880.
- 486 N. Balis, D. Konios, E. Stratakis and E. Kymakis, *Chem-NanoMat*, 2015, **1**, 346–352.
- 487 M. M. Stylianakis, D. Konios, C. Petridis, G. Kakavelakis, E. Stratakis and E. Kymakis, *2D Mater.*, 2017, **4**, 042005.
- 488 N. Balis, E. Stratakis and E. Kymakis, *Mater. Today*, 2016, **19**, 580–594.
- 489 D. Konios, G. Kakavelakis, C. Petridis, K. Savva, E. Stratakis and E. Kymakis, *J. Mater. Chem. A*, 2016, **4**, 1612–1623.
- 490 E. Singh and H. S. Nalwa, *J. Nanosci. Nanotechnol.*, 2015, **15**, 6237–6278.
- 491 V. C. Tung, J. Kim, L. J. Cote and J. Huang, *J. Am. Chem. Soc.*, 2011, **133**, 9262.
- 492 A. R. B. M. Yusoff, W. J. da Silva, H. P. Kim and J. Jang, *Nanoscale*, 2013, **5**, 11051.
- 493 Y. Chen, W.-C. Lin, J. Liu and L. Dai, *Nano Lett.*, 2014, **14**, 1467.
- 494 J. K. Chang, Y. Y. Huang, D. L. Lin, J. I. Tau, T. H. Chen and M. H. Chen, *Sci. Rep.*, 2020, **10**, 1–12.
- 495 S. H. Park, A. Roy, S. Beaupre, S. Cho, N. Coates, J. S. Moon, D. Moses, M. Leclerc, K. Lee and A. J. Heeger, *Nat. Photonics*, 2009, **3**, 297–302.
- 496 D. S. Hecht, L. Hu and G. Irvin, *Adv. Mater.*, 2011, **23**, 1482.
- 497 J. B. Wu, M. Agrawal, H. A. Becerril, Z. N. Bao, Z. F. Liu, Y. S. Chen and P. Peumans, *ACS Nano*, 2010, **4**, 43.
- 498 W. J. da Silva, H. P. Kim, A. R. B. M. Yusoff and J. Jang, *Nanoscale*, 2013, **5**, 9324.
- 499 B. Paci, D. Bailo, V. Albertini, J. Wright, C. Ferrero, G. D. Spyropoulos, E. Stratakis and E. Kymakis, *Adv. Mater.*, 2013, **25**, 4760.
- 500 T. P. Tyler, R. E. Brock, H. J. Karmel, T. J. Marks and M. C. Hersam, *Adv. Energy Mater.*, 2011, **1**, 785.
- 501 E. Kymakis, E. Stratakis, E. Koudoumas and C. Fotakis, *IEEE Trans. Electron Devices*, 2011, **58**, 860.
- 502 S. De, T. M. Higgins, P. E. Lyons, E. M. Doherty, P. N. Nirmalraj, W. J. Blau, J. J. Boland and J. N. Coleman, *ACS Nano*, 2009, **3**, 1767.
- 503 S. I. Na, S. S. Kim, J. Jo and D. Y. Kim, *Adv. Mater.*, 2008, **20**, 4061.



- 504 Y. Wang, S. W. Tong, X. F. Xu, B. Ozyimaz and K. P. Loh, *Adv. Mater.*, 2011, **23**, 1514.
- 505 H. Park, S. Chang, X. Zhou, J. Kong, T. Palacios and S. Gradečak, *Nano Lett.*, 2014, **14**, 5148–5154.
- 506 A. R. Yusoff, D. Kim, F. K. Schneider, W. J. da Silva and J. Jang, *Energy Environ. Sci.*, 2015, **8**, 1523–1537.
- 507 X. Li, Y. Zhu, W. Cai, M. Borysiak, B. Han, D. Chen, R. D. Piner, L. Colombo and R. S. Ruoff, *Nano Lett.*, 2009, **9**, 4359.
- 508 K. S. Kim, Y. Zhao, H. Jang, S. Y. Lee, J. M. Kim, K. S. Kim, J. H. Ahn, P. Kim, J. Y. Choi and B. H. Hong, *Nature*, 2009, **457**, 706.
- 509 B. Bae, H. Kim, Y. Lee, X. F. Xu, J. S. Park, Y. Zheng, J. Balakrishnan, T. Lei, H. R. Kim, Y. I. Song, Y. J. Kim, K. S. Kim, B. Ozyilmaz, J. H. Ahn, B. H. Hong and S. Iijima, *Nat. Nanotechnol.*, 2010, **5**, 574–578.
- 510 S. Park, J. An, J. R. Potts, A. Velamakanni, S. Murali and R. S. Ruoff, *Carbon*, 2011, **49**, 3019.
- 511 E. Kymakis, C. Petridis, T. D. Anthopoulos and E. Stratakis, *IEEE J. Sel. Top. Quantum Electron.*, 2014, **20**, 6573325.
- 512 D. Konios, M. M. Stylianakis, E. Stratakis and E. Kymakis, *J. Colloid Interface Sci.*, 2014, **430**, 108.
- 513 Y. Xu, G. Long, L. Huang, Y. Huang, X. Wan, Y. Ma and Y. Chen, *Carbon*, 2010, **48**, 3308.
- 514 E. Kymakis, E. Stratakis, M. M. Stylianakis, E. Koudoumas and C. Fotakis, *Thin Solid Films*, 2011, **520**, 1238.
- 515 Z. Yin, S. Sun, T. Salim, S. Wu, X. Huang, Q. He, Y. M. Lam and H. Zhang, *ACS Nano*, 2010, **4**, 5263.
- 516 J. Geng, L. Liu, S. B. Yang, S. C. Youn, D. W. Kim, J. S. Lee, J. K. Choi and H. T. Jung, *J. Phys. Chem. C*, 2010, **114**, 14433.
- 517 E. Kymakis, K. Savva, M. M. Stylianakis, C. Fotakis and E. Stratakis, *Adv. Funct. Mater.*, 2013, **23**, 2742.
- 518 X. Huang, Z. Yin, S. Wu, X. Qi, Q. He, Q. Zhang, Q. Yan, F. Boey and H. Zhang, *Small*, 2011, **7**, 1876–1902.
- 519 X. Wang and G. Shi, *Energy Environ. Sci.*, 2015, **8**, 790–823.
- 520 H. Wu, L. Hu, M. W. Rowell, D. Kong, J. J. Cha, J. R. McDonough, J. Zhu, Y. Yang, M. D. McGehee and Y. Cui, *Nano Lett.*, 2010, **10**, 4242.
- 521 J. van de Groep, P. Spinelli and A. Polman, *Nano Lett.*, 2012, **12**, 3138.
- 522 J. Zou, H. L. Yip, S. K. Hau and A. K. Y. Jen, *Appl. Phys. Lett.*, 2010, **96**, 203301.
- 523 D. Konios, C. Petridis, G. Kakavelakis, M. Sygletou, K. Savva, E. Stratakis and E. Kymakis, *Adv. Funct. Mater.*, 2015, **25**, 2213–2221.
- 524 S. Yang, A. G. Ricciardulli, S. Liu, R. Dong, M. R. Lohe, A. Becker, M. A. Squillaci, P. Samori, K. Mullen and X. Feng, *Angew. Chem., Int. Ed.*, 2017, **56**, 6669–6675.
- 525 A. G. Ricciardulli, S. Yang, X. Feng and P. W. M. Blom, *ACS Appl. Mater. Interfaces*, 2017, **9**, 25412–25417.
- 526 A. G. Ricciardulli, S. Yang, G.-J. A. H. Wetzelaer, X. Feng and P. W. M. Blom, *Adv. Funct. Mater.*, 2018, **28**, 1706010.
- 527 D. Koo, S. Jung, J. Seo, G. Jeong, Y. Choi, J. Lee, S. M. Lee, Y. Cho, M. Jeong, J. Lee and J. Oh, *Joule*, 2020, **4**, 1021–1034.
- 528 J. Du, D. Zhang, X. Wang, H. Jin, W. Zhang, B. Tong, Y. Liu, P. L. Burn, H. M. Cheng and W. Ren, *Carbon*, 2021, **171**, 350–358.
- 529 V. Raman, J. Jo and H. K. Kim, *Mater. Sci. Semicond. Process.*, 2020, **120**, 105277.
- 530 B. Y. Wang, E. S. Lee, Y. J. Oh and H. W. Kang, *RSC Adv.*, 2017, **7**, 52914–52922.
- 531 J. H. Kang, S. Choi, Y. J. Park, J. S. Park, N. S. Cho, S. Cho, B. Walker, D. S. Choi, J. W. Shin and J. H. Seo, *Carbon*, 2021, **171**, 341–349.
- 532 D. H. Shin, S. W. Seo, J. M. Kim, H. S. Lee and S. H. Choi, *J. Alloys Compd.*, 2018, **744**, 1–6.
- 533 B. Y. Wang, E. S. Lee, Y. J. Oh and H. W. Kang, *RSC Adv.*, 2017, **7**, 52914–52922.
- 534 W. Zhang, W. Song, J. Huang, L. Huang, T. Yan, J. Ge, R. Peng and Z. Ge, *J. Mater. Chem. A*, 2019, **7**, 22021–22028.
- 535 G. Dennler, M. C. Scharber and C. J. Brabec, *Adv. Mater.*, 2009, **21**, 1323.
- 536 P. W. Blom, V. D. Mihailetschi, L. J. A. Koster and D. E. Markov, *Adv. Mater.*, 2007, **19**, 1551.
- 537 H. Hoppe and N. S. Sariciftci, *J. Mater. Chem.*, 2016, **16**, 45.
- 538 C. J. Brabec, S. Gowrisanker, J. J. Halls, D. Laird, S. Jia and S. P. Williams, *Adv. Mater.*, 2010, **22**, 3839.
- 539 S. Günes, H. Neugebauer and N. S. Sariciftci, *Chem. Rev.*, 2007, **107**, 1324–1338.
- 540 O. Ostroverkhova, *Chem. Rev.*, 2016, **116**, 13279.
- 541 Y. J. Cheng, S. H. Yang and C. S. Hsu, *Chem. Rev.*, 2009, **109**, 5868–5923.
- 542 L. Dou, J. You, Z. Hong, Z. Xu, G. Li, R. A. Street and Y. Yang, *Adv. Mater.*, 2013, **25**, 6642–6671.
- 543 J. E. Anthony, *Chem. Mater.*, 2011, **23**, 583.
- 544 J. C. Bijleveld, R. A. M. Verstrijden, M. M. Wienk and R. A. Janssen, *Appl. Phys. Lett.*, 2010, **97**, 073304.
- 545 T. Liu and A. Troisi, *Adv. Mater.*, 2013, **25**, 1038.
- 546 G. Sauvé and R. Fernando, *J. Phys. Chem. Lett.*, 2015, **6**, 3770.
- 547 L. J. A. Koster, V. D. Mihailetschi and P. W. M. Blom, *Appl. Phys. Lett.*, 2006, **88**, 093511.
- 548 Y. He and Y. Li, *Phys. Chem. Chem. Phys.*, 2011, **13**, 1970–1983.
- 549 Z. Liu, Q. Liu, Y. Huang, Y. Ma, S. Yin, X. Zhang, W. Sun and Y. Chen, *Adv. Mater.*, 2008, **20**, 3924–3930.
- 550 X. F. Zhang and Q. Xi, *Carbon*, 2011, **49**, 3842–3850.
- 551 Y. Li, Y. Hu, Y. Zhao, G. Shi, L. Deng, Y. Hou and L. Qu, *Adv. Mater.*, 2011, **23**, 776–780.
- 552 Q. Liu, Z. Liu, X. Zhang, N. Zhang, L. Yang, S. Yin and Y. Chen, *Appl. Phys. Lett.*, 2008, **92**, 195.
- 553 S. Li, L. YeW Zhao, S. Zhang, S. Mukherjee, H. Ade and J. Hou, *Adv. Mater.*, 2016, **28**, 9423.
- 554 W. Zhao, D. Qian, S. Zhang, S. Li, O. Inganäs, F. Gao and J. Hou, *Adv. Mater.*, 2016, **28**, 4734.
- 555 Y. Yang, Z. G. Zhang, H. Bin, S. Chen, L. Gao, L. Xue, C. Yan and Y. Li, *J. Am. Chem. Soc.*, 2016, **138**, 15011.
- 556 H. Li, T. Earmme, G. Ren, A. Saeki, S. Yoshikawa, N. M. Murari, S. Subramaniam, M. J. Crane, S. Seki and S. A. Jenekhe, *J. Am. Chem. Soc.*, 2014, **136**, 14589.



- 557 F. E. Ala'a, J. P. Sun, I. G. Hill and G. C. Welch, *J. Mater. Chem. A*, 2014, **2**, 1201.
- 558 C. B. Nielsen, S. Holliday, H. Y. Chen, S. J. Cryer and I. McCulloch, *Acc. Chem. Res.*, 2015, **48**, 2803.
- 559 P. Sonar, J. P. F. Lim and K. L. Chan, *Energy Environ. Sci.*, 2011, **4**, 1558.
- 560 Q. Liu, Z. F. Liu, X. Y. Zhang, L. Y. Yang, N. Zhang, G. P. Pan, S. G. Yin, Y. S. Chen and J. Wei, *Adv. Funct. Mater.*, 2009, **19**, 894–904.
- 561 D. Yu, Y. Yang, M. Durstock, J. B. Baek and L. Dai, *ACS Nano*, 2010, **4**, 5633–5640.
- 562 C. M. Hill, Y. Zhu and S. Pan, *ACS Nano*, 2011, **2**, 942–951.
- 563 Z. Liu, Q. Liu, Y. Huang, Y. Ma, S. Yin, X. Zhang, W. Sun and Y. Chen, *Adv. Mater.*, 2008, **20**, 3924–3930.
- 564 V. Gupta, N. Chaudhary, R. Srivastava, G. D. Sharma, R. Bhardwaj and S. Chand, *J. Am. Chem. Soc.*, 2011, **133**, 9960–9963.
- 565 D. Yu, K. Park, M. Durstock and L. Dai, *J. Phys. Chem. Lett.*, 2011, **2**, 1113–1118.
- 566 M. M. Stylianakis, G. D. Spyropoulos, E. Stratakis and E. Kymakis, *Carbon*, 2012, **50**, 5554–5561.
- 567 M. M. Stylianakis, M. Sygletou, K. Savva, G. Kakavelakis, E. Kymakis and E. Stratakis, *Adv. Opt. Mater.*, 2015, **5**, 658–666.
- 568 H.-W. Cho, W.-P. Liao, W.-H. Lin, M. Yoshimura and J.-J. Wu, *J. Power Sources*, 2015, **293**, 246–252.
- 569 Z. G. Zhang, Y. Bai and Y. Li, *Chin. J. Polym. Sci.*, 2021, **39**, 1–13.
- 570 T. Ameri, P. Khoram, J. Min and C. J. Brabec, *Adv. Mater.*, 2013, **25**, 4245–4266.
- 571 P. Cheng, Y. Lia and X. Zhang, *Energy Environ. Sci.*, 2014, **7**, 2005.
- 572 S. Belviso, A. Capasso, E. Santoro, L. Najafi, F. Lelj, S. Superchi, D. Casarini, C. Villani, D. Spirito, S. Bellani, A. E. Del Rio Del Rio-Castillo and F. Bonaccorso, *Adv. Funct. Mater.*, 2018, **28**, 1705418.
- 573 G. H. Jun, S. H. Jin, B. Lee, B. H. Kim, W.-S. Chae, S. H. Hong and S. Jeon, *Energy Environ. Sci.*, 2013, **6**, 3000–3006.
- 574 P. Robaey, F. Bonaccorso, E. Bourgeois, J. D'Haen, W. Dierckx, W. Dexters, D. Spoltore, J. Drijkoningen, J. Liesenborgs, A. Lombardo, A. C. Ferrari, F. Van Reeth, K. Haenen, J. V. Manca and M. Nesladek, *Appl. Phys. Lett.*, 2014, **105**, 083306.
- 575 M. M. Stylianakis, D. Konios, G. Kakavelakis, G. Charalambidis, E. Stratakis, A. G. Coutsolelos, E. Kymakis and S. H. Anastasiadis, *Nanoscale*, 2015, **7**, 17827–17835.
- 576 J. K. Kim, M. J. Park, S. J. Kim, D. H. Wang, S. P. Cho, S. Bae, J. H. Park and B. H. Hong, *ACS Nano*, 2013, **7**, 7207–7212.
- 577 N. Balis, D. Konios, E. Stratakis and E. Kymakis, *Chem-NanoMat*, 2015, **5**, 346–352.
- 578 J.-H. Kim, D. H. Sin, H. Kim, S. B. Jo, H. Lee, J. T. Han and K. Cho, *ACS Appl. Mater. Interfaces*, 2019, **11**, 20183.
- 579 A. Bruno, C. Borriello, S. A. Haque, C. Minarini and T. D. Luccio, *Phys. Chem. Chem. Phys.*, 2014, **16**, 17998–18003.
- 580 M. Sygletou, P. Tzourmpakis, C. Petridis, D. Konios, C. Fotakis, E. Kymakis and E. Stratakis, *J. Mater. Chem. A*, 2016, **4**, 1020–1027.
- 581 K. Sasitharan, D. G. Bossanyi, N. Vaenas, A. J. Parnell, J. Clark, A. Iraqi, D. G. Lidzey and J. A. Foster, *J. Mater. Chem. A*, 2020, **8**, 6067–6075.
- 582 C. Huang and H. Yu, *2D Mater.*, 2020, **7**, 025023.
- 583 W. Yang, L. Ye, F. Yao, C. Jin, H. Ade and H. Chen, *Nano Res.*, 2019, **12**, 777.
- 584 H. C. Wang, Y. C. Lin, C. H. Chen, C. H. Huang, B. Chang, Y. L. Liu, H. W. Cheng, C. S. Tsao and K. H. Wei, *Nanoscale*, 2019, **11**, 17460.
- 585 L. Liu, Y. Kan, K. Gao, J. Wang, M. Zhao, H. Chen, C. Zhao, T. Jiu, A. K. Y. Jen and Y. Li, *Adv. Mater.*, 2020, **32**, 1907604.
- 586 C.-Z. Li, C.-Y. Chang, Y. Zang, H.-X. Ju, C.-C. Chueh, P.-W. Liang, N. Cho, D. S. Ginger and A. K. Y. Jen, *Adv. Mater.*, 2014, **26**, 6262.
- 587 L. Lu, T. Xu, I. H. Jung and L. Yu, *J. Phys. Chem. C*, 2014, **118**, 22834–22839.
- 588 V. Shrotriya, G. Li, Y. Yao, C. Chu and Y. Yang, *Appl. Phys. Lett.*, 2006, **88**, 073508.
- 589 F. Jiang, W. C. H. Choy, X. Li, D. Zhang and J. Cheng, *Adv. Mater.*, 2015, **27**, 2930.
- 590 H. Yan, P. Lee, N. R. Armstrong, A. Graham, G. A. Evmenenko, P. Dutta and T. J. Marks, *J. Am. Chem. Soc.*, 2005, **127**, 3172.
- 591 A. W. Hains and T. J. Marks, *Appl. Phys. Lett.*, 2008, **92**, 023504.
- 592 H. L. Yip, S. K. Hau, N. S. Baek, H. Ma and A. K. Y. Jen, *Adv. Mater.*, 2008, **20**, 2376.
- 593 T. Y. Chu, J. Lu, S. Beaupre, Y. Zhang, J. R. Pouliot, S. Wakim, J. Zhou, M. Leclerc, Z. Li, J. Ding and Y. Tao, *J. Am. Chem. Soc.*, 2011, **133**, 4250.
- 594 M. Jorgensen, K. Norrman and F. C. Krebs, *Sol. Energy Mater. Sol. Cells*, 2008, **92**, 686.
- 595 M. Graetzel, R. A. Janssen, D. B. Mitzi and E. H. Sargent, *Nature*, 2012, **488**, 304.
- 596 X. Wan, G. Long, L. Huang and Y. Chen, *Adv. Mater.*, 2011, **23**, 5342–5358.
- 597 Q. Van, Le, J. Y. Choi and S. Y. Kim, *FlatChem*, 2017, **2**, 54–66.
- 598 Z. Yin, J. Wei and Q. Zheng, *Adv. Sci.*, 2016, **3**, 1500362.
- 599 B. Xu, S. A. Gopalan, A. I. Gopalan, N. Muthuchamy, K. P. Lee, J. S. Lee, Y. Jiang, S. W. Lee, S. W. Kim, J. S. Kim and H. M. Jeong, *Sci. Rep.*, 2017, **7**, 45079.
- 600 K. M. Reza, S. Mabrouk and Q. Qiao, *Proc. Nat. Res. Soc.*, 2018, **2**, 02004.
- 601 H. Frankenstein, C. Z. Leng, M. D. Losego and G. L. Frey, *Org. Electron.*, 2019, **64**, 37–46.
- 602 M. Zafar, J. Y. Yun and D. H. Kim, *Appl. Surf. Sci.*, 2017, **398**, 9–14.
- 603 J. A. Raiford, R. A. Belisle, K. A. Bush, R. Prasanna, A. F. Palmstrom, M. D. McGehee and S. F. Bent, *Sustainable Energy Fuels*, 2019, **3**, 1517–1525.
- 604 W. C. Choy and D. Zhang, *Small*, 2016, **12**, 416–431.



- 605 S.-S. Li, K.-H. Tu, C.-C. Lin, C.-W. Chen and M. Chhowalla, *ACS Nano*, 2010, **4**, 3169.
- 606 J. C. Yu, J. I. Jang, B. R. Lee, G. W. Lee, J. T. Han and M. H. Song, *ACS Appl. Mater. Interfaces*, 2014, **6**, 2067.
- 607 Y.-H. Chao, J.-S. Wu, C.-E. Wu, J.-F. Jheng, C.-L. Wang and C.-S. Hsu, *Adv. Energy Mater.*, 2013, **3**, 1279–1285.
- 608 B. Paci, G. Kakavelakis, A. Generosi, V. Albertini, J. Wright, C. Ferrero, D. Konios, E. Stratakis and E. Kymakis, *RSC Adv.*, 2015, **5**, 106930–106940.
- 609 J.-M. Yun, J.-S. Yeo, J. Kim, H.-G. Jeong, D.-Y. Kim, Y.-J. Noh, S.-S. Kim, B.-C. Ku and S.-I. Na, *Adv. Mater.*, 2011, **23**, 4923–4928.
- 610 I. P. Murray, S. J. Lou, L. J. Cote, S. Loser, C. J. Kadleck, T. Xu, J. M. Szarko, B. S. Rolczynski, J. E. Johns, J. Huang, L. Yu, L. X. Chen, T. J. Marks and M. C. Hersam, *J. Phys. Chem. Lett.*, 2011, **2**, 3006.
- 611 J.-S. Yeo, J.-M. Yun, Y.-S. Jung, D.-Y. Kim, Y.-J. Noh, S.-S. Kim and S.-I. Na, *J. Mater. Chem. A*, 2014, **2**, 292–298.
- 612 J. Liu, Y. Xue and L. Dai, *J. Phys. Chem. Lett.*, 2012, **3**, 1928.
- 613 J. Kim, V. C. Tung and J. Huang, *Adv. Energy Mater.*, 2011, **1**, 1052.
- 614 E. Stratakis, M. M. Stylianakis, E. Koudoumas and E. Kymakis, *Nanoscale*, 2013, **5**, 4144.
- 615 M. Li, W. Ni, B. Kan, X. Wan, L. Zhang, Q. Zhang, G. Long, Y. Zuo and Y. Chen, *Phys. Chem. Chem. Phys.*, 2013, **15**, 18973.
- 616 J. Zhou, X. Wan, Y. Liu, Y. Zuo, Z. Li, G. He, G. Long, W. Ni, C. Li, X. Su and Y. Chen, *J. Am. Chem. Soc.*, 2012, **134**, 16345–16351.
- 617 S.-H. Kim, C.-H. Lee, J.-M. Yun, Y.-J. Noh, S.-S. Kim, S. Lee, S. M. Jo, H.-I. Joh and S.-I. Na, *Nanoscale*, 2014, **6**, 7183.
- 618 C. Li, X. Yang, Y. Zhao, P. Zhang, Y. Tu and Y. Li, *Org. Electron.*, 2014, **15**, 2868.
- 619 E. Stratakis, K. Savva, D. Konios, C. Petridis and E. Kymakis, *Nanoscale*, 2014, **6**, 6925.
- 620 X. Chen, Q. Liu, M. Zhang, H. Ju, J. Zhu, Q. Qiao, M. Wang and S. Yang, *Nanoscale*, 2018, **10**, 14840.
- 621 X. Gu, W. Cui, H. Li, Z. Wu, Z. Zeng, S.-T. Lee, H. Zhang and B. Sun, *Adv. Energy Mater.*, 2013, **3**, 1262.
- 622 J.-M. Yun, Y.-J. Noh, J.-S. Yeo, Y.-J. Go, S.-I. Na, H.-G. Jeong, J. Kim, S. Lee, S.-S. Kim, H. Y. Koo, T.-W. Kim and D.-Y. Kim, *J. Mater. Chem. C*, 2013, **1**, 3777.
- 623 Q. V. Le, T. P. Nguyen, H. W. Jang and S. Y. Kim, *Phys. Chem. Chem. Phys.*, 2014, **16**, 13123.
- 624 X. Yang, W. Fu, W. Liu, J. Hong, Y. Cai, C. Jin, M. Xu, H. Wang, D. Yang and H. Chen, *J. Mater. Chem. A*, 2014, **2**, 7727–7733.
- 625 W. Liu, X. Yang, Y. Zhang, M. Xu and H. Chen, *RSC Adv.*, 2014, **4**, 32744.
- 626 X. Yang, W. Liu, M. Xiong, Y. Zhang, T. Liang, J. Yang, M. Xu, J. Ye and H. Chen, *J. Mater. Chem. A*, 2014, **2**, 14798.
- 627 A. Foti, C. D'Andrea, F. Bonaccorso, M. Lanza, G. Calogero, E. Messina, O. M. Maragò, B. Fazio and P. G. Gucciardi, *Plasmonics*, 2013, **8**, 13.
- 628 F. Bonaccorso, M. Zerbetto, A. C. Ferrari and V. Amendola, *J. Phys. Chem. C*, 2013, **117**, 13217.
- 629 X. Zheng, H. Zhang, Q. Yang, C. Xiong, W. Li, Y. Yan, R. S. Gurney and T. Wang, *Carbon*, 2019, **142**, 156.
- 630 K. C. Kwon, C. Kim, Q. V. Le, S. Gim, J. M. Jeon, J. Y. Ham, J. L. Lee, H. W. Jang and S. W. Kim, *ACS Nano*, 2015, **9**, 4146.
- 631 Q. V. Le, T. P. Nguyen, K. S. Choi, Y.-H. Cho, Y. J. Hong and S. Y. Kim, *Phys. Chem. Chem. Phys.*, 2014, **16**, 25468.
- 632 X. Gu, W. Cui, T. Song, C. Liu, X. Shi, S. Wang and B. Sun, *ChemSusChem*, 2014, **7**, 416.
- 633 Z. Yuan, Z. Wu, S. Bai, W. Cui, J. Liu, T. Song and B. Sun, *Org. Electron.*, 2015, **26**, 327.
- 634 Y. Lin, B. Adilbekova, Y. Firdaus, E. Yengel, H. Faber, M. Sajjad, X. Zheng, E. Yarali, A. Seitzkhan, O. M. Bakr, A. El-Labban, U. Schwingenschlöggl, V. Tung, I. McCulloch, F. Laquai and T. D. Anthopoulos, *Adv. Mater.*, 2019, **31**, 1902965.
- 635 W. Zhao, S. Li, H. Yao, S. Zhang, Y. Zhang, B. Yang and J. Hou, *J. Am. Chem. Soc.*, 2017, **139**, 7148.
- 636 M. Zhang, X. Guo, W. Ma, H. Ade and J. Hou, *Adv. Mater.*, 2015, **27**, 4655–4660.
- 637 J. Liu, Y. Xue, Y. Gao, D. Yu, M. Durstock and L. Dai, *Adv. Mater.*, 2012, **24**, 2228–2233.
- 638 H. B. Yang, Y. Q. Dong, X. Wang, S. Y. Khoo and B. Liu, *ACS Appl. Mater. Interfaces*, 2014, **6**, 1092.
- 639 G. Kakavelakis, D. Konios, E. Stratakis and E. Kymakis, *Chem. Mater.*, 2014, **26**, 5988.
- 640 S. Pandey, M. Karakoti, N. Chaudhary, S. Gupta, A. Kumar, S. Dhali, A. Patra, R. K. Singh and N. G. Sahoo, *J. Nanosci. Nanotechnol.*, 2020, **20**, 3888.
- 641 Q. Yang, S. Yu, P. Fu, W. Yu, Y. Liu, X. Liu, Z. Feng, X. Guo and C. Li, *Adv. Funct. Mater.*, 2020, **30**, 1910205.
- 642 J. Wang, H. Yu, C. Hou and J. Zhang, *Sol. RRL*, 2020, **4**, 1900428.
- 643 B. Adilbekova, Y. Lin, E. Yengel, H. Faber, G. Harrison, Y. Firdaus, A. El-Labban, D. H. Anjum, V. Tung and T. D. Anthopoulos, *J. Mater. Chem. C*, 2020, **8**, 5259–5264.
- 644 K. D. G. I. Jayawardena, R. Rhodes, K. K. Gandhi, M. R. R. Prabhath, G. D. M. R. Dabera, M. J. Beliatas, L. J. Rozanski, S. J. Henley and S. R. P. Silva, *J. Mater. Chem. A*, 2013, **1**, 9922.
- 645 M. J. Beliatas, K. K. Gandhi, L. J. Rozanski, R. Rhodes, L. McCafferty, M. R. Alenezi, A. S. Alshammari, C. A. Mills, K. D. Jayawardena, S. J. Henley and S. R. Silva, *Adv. Mater.*, 2014, **26**, 2078.
- 646 Y. Zhang, S. Yuan, Y. Li and W. Zhang, *Electrochim. Acta*, 2014, **117**, 438.
- 647 Y. Zhang, S. Yuan and W. Liu, *Electrochim. Acta*, 2014, **143**, 18.
- 648 S. Qu, M. Li, L. Xie, X. Huang, J. Yang, N. Wang and S. Yang, *ACS Nano*, 2013, **7**, 4070.
- 649 H. Xu, L. Zhang, Z. Ding, J. Hu, J. Liu and Y. Liu, *Nano Res.*, 2018, **11**, 4293–4301.
- 650 S. Lin, S. Liu, Z. Yang, Y. Li, T. W. Ng, Z. Xu, Q. Bao, J. Hao, C. S. Lee, C. Surya, F. Yan and S. P. Lau, *Adv. Funct. Mater.*, 2016, **26**, 864–871.



- 651 D. Konios, G. Kakavelakis, C. Petridis, K. Sawva, E. Stratakis and E. Kymakis, *J. Mater. Chem. A*, 2016, **4**, 1612–1623.
- 652 Z. Yu, W. Feng, W. Lu, B. Li, H. Yao, K. Zeng and J. Ouyang, *J. Mater. Chem. A*, 2019, **7**, 11160.
- 653 F. Pan, C. Sun, Y. Li, D. Tang, Y. Zou, X. Li, S. Bai, X. Wei, M. Lv, X. Chen and Y. Li, *Energy Environ. Sci.*, 2019, **12**, 3400.
- 654 K. S. Lee, Y. J. Park, J. Shim, C. H. Lee, G. H. Lim, H. Y. Kim, J. W. Choi, C. L. Lee, Y. Jin, K. Yu, H. S. Chung, B. Angadi, S. I. Nah and D. I. Son, *J. Mater. Chem. A*, 2019, **7**, 15356.
- 655 T. Förster, *Ann. Phys.*, 1948, **437**, 55.
- 656 P. H. Tan, T. Hasan, F. Bonaccorso, V. Scardaci, A. G. Rozhin, W. I. Milne and A. C. Ferrari, *Phys. E*, 2008, **40**, 2352.
- 657 J. You, L. Dou, Z. Hong, G. Li and Y. Yang, *Prog. Polym. Sci.*, 2013, **38**, 1909.
- 658 Y. Cui, H. Yao, B. Gao, Y. Qin, S. Zhang, B. Yang, C. He, B. Xu and J. Hou, *J. Am. Chem. Soc.*, 2017, **139**, 7302–7309.
- 659 K. Zhang, B. Fan, R. Xia, X. Liu, Z. Hu, H. Gu, S. Liu, H. L. Yip, L. Ying, F. Huang and Y. Cao, *Adv. Energy Mater.*, 2018, **8**, 1703180.
- 660 C. C. Chueh, C. Z. Li and A. K. Y. Jen, *Energy Environ. Sci.*, 2015, **8**, 1160.
- 661 J. Y. Kim, K. Lee, N. E. Coates, D. Moses, T. Q. Nguyen, M. Dante and A. J. Heeger, *Science*, 2007, **317**, 222.
- 662 W. Li, A. Furlan, K. H. Hendriks, M. M. Wienk and R. A. J. Janssen, *J. Am. Chem. Soc.*, 2013, **135**, 5529.
- 663 A. Hadipour, B. de Boer, J. Wildeman, F. B. Kooistra, J. C. Hummelen, M. G. R. Turbiez, M. M. Wienk, R. A. J. Janssen and P. W. M. Blom, *Adv. Funct. Mater.*, 2006, **16**, 1897–1903.
- 664 M. P. De Jong, L. J. van IJzendoorn and M. J. A. de Voigt, *Appl. Phys. Lett.*, 2000, **77**, 2255–2257.
- 665 V. C. Tung, J. Kim, L. J. Cote and J. Huang, *J. Am. Chem. Soc.*, 2011, **133**, 9262.
- 666 Y. Chen, W.-C. Lin, J. Liu and L. Dai, *Nano Lett.*, 2014, **14**, 1467.
- 667 J. Guo and J. Min, *Adv. Energy Mater.*, 2019, **9**, 1802521.
- 668 L. X. Chen, *ACS Energy Lett.*, 2019, **4**, 2537–2539.
- 669 S. Jeong, B. Park, S. Hong, S. Kim, J. Kim, S. Kwon, J. H. Lee, M. S. Lee, J. C. Park, H. Kang and K. Lee, *ACS Appl. Mater. Interfaces*, 2020, **12**, 41877–41885.
- 670 S. I. Na, Y. H. Seo, Y. C. Nah, S. S. Kim, H. Heo, J. Kim, E. Rolston, R. H. Dauskardt, M. Gao, Y. Lee and D. Vak, *Adv. Funct. Mater.*, 2019, **29**, 1805825.
- 671 Y. Lin, Y. Jin, S. Dong, W. Zheng, J. Yang, A. Liu, F. Liu, Y. Jiang, T. P. Russell, F. Zhang, F. Huang and L. Hou, *Adv. Energy Mater.*, 2018, **8**, 1701942.
- 672 S. Rasool, D. V. Vu, C. E. Song, H. K. Lee, S. K. Lee, J. C. Lee, S. J. Moon and W. S. Shin, *Adv. Energy Mater.*, 2019, **9**, 1900168.
- 673 S. Song, K. T. Lee, C. W. Koh, H. Shin, M. Gao, H. Woo, D. Vak and J. Y. Kim, *Energy Environ. Sci.*, 2018, **11**, 3248–3255.
- 674 T. Yan, W. Song, J. Huang, R. Peng, L. Huang and Z. Ge, *Adv. Mater.*, 2019, **31**, 1902210.
- 675 X. Chen, G. Xu, G. Zeng, H. Gu, H. Chen, H. Xu, H. Yao, Y. Li, J. Hou and Y. Li, *Adv. Mater.*, 2020, **32**, 1908478.
- 676 Y. W. Han, S. J. Jeon, H. S. Lee, H. Park, K. S. Kim, H. W. Lee and D. K. Moon, *Adv. Energy Mater.*, 2019, **9**, 1902065.
- 677 Y. X. Zhang, J. Fang, W. Li, Y. Shen, J. D. Chen, Y. Li, H. Gu, S. Pelivani, M. Zhang, Y. Li and J. X. Tang, *ACS Nano*, 2019, **13**, 4686–4694.
- 678 W. Zhang, W. Song, J. Huang, L. Huang, T. Yan, J. Ge, R. Peng and Z. Ge, *J. Mater. Chem. A*, 2019, **7**, 22021–22028.
- 679 L. Meng, Y. Zhang, X. Wan, C. Li, X. Zhang, Y. Wang, X. Ke, Z. Xiao, L. Ding, R. Xia and H. L. Yip, *Science*, 2018, **361**, 1094–1098.
- 680 M. Jošt, L. Kegelmann, L. Korte and S. Albrecht, *Adv. Energy Mater.*, 2020, **10**, 1904102.
- 681 S. Park, H. Ahn, J. Y. Kim, J. B. Park, J. Kim, S. H. Im and H. J. Son, *ACS Energy Lett.*, 2019, **5**, 170–179.
- 682 R. Singh, C. L. Chochos, V. G. Gregoriou, V. D. Nega, M. Kim, M. Kumar, S. C. Shin, S. H. Kim, J. W. Shim and J. J. Lee, *ACS Appl. Mater. Interfaces*, 2019, **11**, 36905–36916.
- 683 Y. Cho, T. Kumari, S. Jeong, S. M. Lee, M. Jeong, B. Lee, J. Oh, Y. Zhang, B. Huang, L. Chen and C. Yang, *Nano Energy*, 2020, **75**, 104896.
- 684 M. S. Ahmad, A. K. Pandey and N. A. Rahim, *Renewable Sustainable Energy Rev.*, 2017, **77**, 89–108.
- 685 J. Gong, J. Liang and K. Sumathy, *Renewable Sustainable Energy Rev.*, 2012, **16**, 5848–5860.
- 686 A. Nathan, A. Ahnood, M. T. Cole, S. Lee, Y. Suzuki, P. Hiralal, F. Bonaccorso, T. Hasan, L. Garcia-Gancedo, A. Dyadyusha, S. Haque, P. Andrew, S. Hofmann, J. Moultrie, D. Chu, A. J. Flewitt, A. C. Ferrari, M. J. Kelly, J. Robertson, G. A. J. Amaratunga and W. I. Milne, *Proc. IEEE*, 2012, **100**, 1486.
- 687 A. Hagfeldt, G. Boschloo, L. Sun, L. Kloo and H. Pettersson, *Chem. Rev.*, 2010, **110**, 6595–6663.
- 688 M. K. Nazeeruddin, P. Liska, J. Moser, N. Vlachopoulos and M. Grätzel, *Helv. Chim. Acta*, 1990, **73**, 1788–1803.
- 689 S. M. Feldt, E. A. Gibson, E. Gabrielsson, L. Sun, G. Boschloo and A. Hagfeldt, *J. Am. Chem. Soc.*, 2010, **132**(46), 16714–16724.
- 690 U. Bach, D. Lupo, P. Comte, J. E. Moser, F. Weissortel, J. Salbeck, H. Spreitzer and M. Gratzel, *Nature*, 1998, **395**, 583–585.
- 691 J. Wu, Z. Lan, S. Hao, P. Li, J. Lin, M. Huang, L. Fang and Y. Huang, *Pure Appl. Chem.*, 2008, **80**, 2241–2258.
- 692 B. Li, L. Wang, B. Kang, P. Wang and Y. Qiu, *Sol. Energy Mater. Sol. Cells*, 2006, **90**, 549–573.
- 693 W. Zhang, Y. Wu, H. W. Bahng, Y. Cao, C. Yi, Y. Saygili, J. Luo, Y. Liu, L. Kavan, J.-E. Moser, A. Hagfeldt, H. Tian, S. M. Zakeeruddin, W.-H. Zhu and M. Grätzel, *Energy Environ. Sci.*, 2018, **11**, 1779–1787.
- 694 N. Papageorgiou, *Coord. Chem. Rev.*, 2004, **248**, 1421–1446.
- 695 K. Li, Z. Yu, Y. Luo, D. Li and Q. Meng, *J. Mater. Sci. Technol.*, 2007, **23**, 577–582.
- 696 M. Gratzel, *Inorg. Chem.*, 2005, **44**, 6841–6851.
- 697 B. E. Hardin, H. J. Snaith and M. D. McGehee, *Nat. Photonics*, 2012, **6**, 162–169.



- 698 J. D. Roy-Mayhew and I. A. Aksay, *Chem. Rev.*, 2014, **114**, 6323–6348.
- 699 E. Singh and H. S. Nalwa, *Sci. Adv. Mater.*, 2015, **7**, 1863–1912.
- 700 D. W. Zhang, X. D. Li, H. B. Li, S. Chen, Z. Sun, X. J. Yin and S. M. Huang, *Carbon*, 2011, **49**, 5382–5388.
- 701 H. Choi, H. Kim, S. Hwang, W. Choi and M. Jeon, *Sol. Energy Mater. Sol. Cells*, 2011, **95**, 323–325.
- 702 X. Wang, L. Zhi and K. Müllen, *Nano Lett.*, 2008, **8**, 323–327.
- 703 X. Yan, X. Cui, B. Li and I.-S. Li, *Nano Lett.*, 2010, **10**, 1869–1873.
- 704 N. Yang, J. Zhai, D. Wang, Y. Chen and L. Jiang, *ACS Nano*, 2010, **4**, 887–894.
- 705 T. Chen, W. Hu, J. Song, G. H. Guai and C. M. Li, *Adv. Funct. Mater.*, 2012, **22**, 5245–5250.
- 706 C. Chen, M. Long, M. Xia, C. Zhang and W. Cai, *Nanoscale Res. Lett.*, 2012, **7**, 101.
- 707 Y. H. Ng, I. V. Lightcap, K. Goodwin, M. Matsumura and P. V. Kamat, *J. Phys. Chem. Lett.*, 2010, **1**, 2222–2227.
- 708 Z. Peining, A. S. Nair, P. Shengjie, Y. Shengyuan and S. Ramakrishna, *ACS Appl. Mater. Interfaces*, 2012, **4**, 581–585.
- 709 H. Wang, S. L. Leonard and Y. H. Hu, *Ind. Eng. Chem. Res.*, 2012, **51**, 10613–10620.
- 710 J. Durantini, P. P. Boix, M. Gervaldo, G. M. Morales, L. Otero, J. Bisquert and E. M. Barea, *J. Electroanal. Chem.*, 2012, **683**, 43–46.
- 711 M.-H. Jung, M. G. Kang and M.-J. Chu, *J. Mater. Chem.*, 2012, **22**, 16477–16483.
- 712 I. Ahmad, U. Khan and Y. K. Gun'ko, *J. Mater. Chem.*, 2011, **21**, 16990–16996.
- 713 J. D. Roy-Mayhew, D. J. Bozym, C. Punckt and I. A. Aksay, *ACS Nano*, 2010, **4**, 6203–6211.
- 714 L. Kavan, J. H. Yum and M. Gratzel, *ACS Nano*, 2010, **5**, 165–172.
- 715 S. Pang, Y. Hernandez, X. Feng and K. Mullen, *Adv. Mater.*, 2011, **23**, 2779–2795.
- 716 A. Andersson, N. Johansson, P. Broms, N. Yu, D. Lupo and W. R. Salaneck, *Adv. Mater.*, 1998, **10**, 859–863.
- 717 M. G. Helander, M. T. Greiner, Z. B. Wang and W. M. Tang, *J. Vac. Sci. Technol., A*, 2011, **29**, 011019.
- 718 N. L. Yang, J. Zhai, D. Wang, Y. S. Chen and L. Jiang, *ACS Nano*, 2010, **4**, 887–894.
- 719 Z. Y. Banyamin, P. J. Kelly, G. West and J. Boardman, *Coatings*, 2014, **4**, 732–746.
- 720 <http://minerals.usgs.gov/minerals/pubs/commodity/indium/>.
- 721 N. Chantarat, Y. W. Chen, S. H. Hsu, C. C. Lin, M. C. Chiang and S. Y. Chen, *ECS J. Solid State Sci. Technol.*, 2013, **2**, 131–135.
- 722 H. A. Becerril, J. Mao, Z. Liu, R. M. Stoltenberg, Z. Bao and Y. Chen, *ACS Nano*, 2008, **2**, 463–470.
- 723 H. Sun, A. Varzi, V. Pellegrini, D. A. Dinh, R. Raccichini, A. E. Del Rio-Castillo, M. Prato, M. Colombo, R. Cingolani, B. Scrosati, S. Passerini and F. Bonaccorso, *Solid State Commun.*, 2017, **251**, 88.
- 724 Y. Gao, W. Shi, W. Wang, Y. Leng and Y. Zhao, *Ind. Eng. Chem. Res.*, 2014, **53**, 16777–16784.
- 725 F. T. Kong, S. Y. Dai and K. J. Wang, *Adv. Optoelectron.*, 2007, 75384.
- 726 D. Sengupta, P. Das, B. Mondal and K. Mukherjee, *Renewable Sustainable Energy Rev.*, 2016, **60**, 356–376.
- 727 M. Law, L. Green, J. Johnson, R. Saykally and P. Yang, *Nat. Mater.*, 2005, **4**, 455–459.
- 728 J. Baxter, A. Walker, K. Van Ommering and E. Aydil, *Nanotechnology*, 2006, **17**, S304–S312.
- 729 H. Y. Chen, D. B. Kuang and C. Y. Su, *J. Mater. Chem.*, 2012, **22**, 15475–15489.
- 730 F. Xu and L. Sun, *Energy Environ. Sci.*, 2011, **4**, 818–841.
- 731 T. Prakash, *Electron. Mater. Lett.*, 2012, **8**, 231–243.
- 732 A. E. R. Mohamed and S. Rohani, *Energy Environ. Sci.*, 2011, **4**, 1065–1086.
- 733 F. T. Kong and S. Y. Dai, *Prog. Chem.*, 2006, **18**, 1409–1424.
- 734 L. Passoni, F. Fumagalli, A. Perego, S. Bellani, P. Mazzolini and F. Di Fonzo, *Nanotechnology*, 2017, **28**, 245603.
- 735 P. Avouris, *Nano Lett.*, 2010, **10**, 4285–4294.
- 736 T. Chu and Z. Chen, *ACS Nano*, 2014, **8**, 3584–3589.
- 737 C. Gong, S. McDonnell, X. Qin, A. Azcatl, H. Dong, Y. J. Chabal, K. Cho and R. M. Wallace, *ACS Nano*, 2014, **8**, 642–649.
- 738 C. Liu, Y. Xu and Y. Y. Noh, *Mater. Today*, 2015, **18**, 79–96.
- 739 T. Cusati, G. Fiori, A. Gahoi, V. Passi, M. C. Lemme, A. Fortunelli and G. Iannaccone, *Sci. Rep.*, 2017, **7**, 5109.
- 740 S. Sun, L. Gao and Y. Liu, *Appl. Phys. Lett.*, 2010, **96**, 083113.
- 741 Y. Kusumawati, M. A. Martoprawiro and T. H. Pauporté, *J. Phys. Chem. C*, 2014, **118**, 9974–9981.
- 742 A. Sacco, S. Porro, A. Lamberti, M. Gerosa, M. Castellino, A. Chiodoni and S. Bianco, *Electrochim. Acta*, 2014, **131**, 154–159.
- 743 H. Ding, S. Zhang, J.-T. Chen, X.-P. Hu, Z.-F. Du, Y.-X. Qiu and D.-L. Zhao, *Thin Solid Films*, 2015, **584**, 29–36.
- 744 H. X. Wang, Q. Wang, K.-G. Zhou and H.-L. Zhang, *Small*, 2013, **9**, 1266–1283.
- 745 D. Chen, H. Zhang, Y. Liu and J. H. Li, *Energy Environ. Sci.*, 2013, **6**, 1362–1387.
- 746 J. Macaira, L. Andrade and A. Mendes, *Renewable Sustainable Energy Rev.*, 2013, **27**, 334–349.
- 747 M. Ye, X. Wen, M. Wang, J. Iocozzia, N. Zhang, C. Lin and Z. Lin, *Mater. Today*, 2015, **18**, 155–162.
- 748 G. Zhu, P. Likun, S. Hengchao, X. Liu, T. Lv, N. Zhou and Z. Sun, *Nanosci. Nanotechnol. Lett.*, 2013, **5**, 154–158.
- 749 X. Yu, D. Lin, P. Li and Z. Su, *Sol. Energy Mater. Sol. Cells*, 2017, **172**, 252–269.
- 750 F. W. Low and C. W. Lai, *Renewable Sustainable Energy Rev.*, 2018, **82**, 103–125.
- 751 V. Štengl, S. Bakardjieva, T. M. Grygar, J. Bludská and M. Kormunda, *Chem. Cent. J.*, 2013, **7**, 41.
- 752 V. Štengl, D. Popelková and P. Vlácil, *J. Phys. Chem. C*, 2011, **115**, 25209.
- 753 F. Xu, J. Chen, X. Wu, Y. Zhang, Y. Wang, J. Sun, H. Bi, W. Lei, Y. Ni and L. Sun, *J. Phys. Chem. C*, 2013, **117**, 8619–8627.



- 754 Y. Liu, L. Gao, J. Sun, Y. Wang and J. Zhang, *Nanotechnology*, 2009, **20**, 465605.
- 755 T.-H. Tsai, S.-C. Chiou and S.-M. Chen, *Int. J. Electrochem. Sci.*, 2011, **6**, 3333–3343.
- 756 H. Hayashi, I. V. Lightcap, M. Tsujimoto, M. Takano, T. Umeyama, P. V. Kamat and H. Imahori, *J. Am. Chem. Soc.*, 2011, **133**, 7684–7687.
- 757 X. Fang, Li, K. Guo, Y. Zhu, Z. Hu, X. Liu, B. Chen and X. Zhao, *Electrochim. Acta*, 2012, **65**, 174–178.
- 758 Y.-B. Tang, C.-Sing Lee, J. Xu, Z.-Tao Liu, Z.-H. Chen, Z. He, Y.-L. Cao, G. Yuan, H. Song, L. Chen, L. Luo, H.-M. Cheng, W.-J. Zhang, I. Bello and S.-T. Lee, *ACS Nano*, 2010, **4**, 3482–3488.
- 759 L.-C. Chen, C.-H. Hsu, P.-S. Chan, X. Zhang and C.-J. Huang, *Nanoscale Res. Lett.*, 2014, **9**, 380.
- 760 Z. Xiang, X. Zhou, G. Wan, G. Zhang and D. Cao, *ACS Sustainable Chem. Eng.*, 2014, **2**, 1234–1240.
- 761 G. Eda, J. Ball, C. Mattevi, M. Acik, L. Artiglia, G. Granozzi, Y. Chabal, T. D. Anthopoulos and M. Chhowalla, *J. Mater. Chem.*, 2011, **21**, 11217–11223.
- 762 U. Mehmood, S. Ahmed, I. A. Hussein and K. Harrabi, *Photonics Nanostruct.: Fundam. Appl.*, 2015, **16**, 34–42.
- 763 G. Cicero, G. Musso, A. Lamberti, B. Camino, S. Bianco, D. Pugliese, F. Risplendi, A. Sacco, N. Shahzad, A. M. Ferrari, B. Ballarin, C. Barolo, E. Tresso and G. Caputo, *Phys. Chem. Chem. Phys.*, 2013, **15**, 7198–7203.
- 764 J. He, D. Wu, Z. Gao, F. Xu, S. Jiang, S. Zhang, K. Cao, Y. Guo and K. Jiang, *RSC Adv.*, 2014, **4**, 2068–2072.
- 765 P. Ranganathan, R. Sasikumar, S.-M. Chen, S.-P. Rwei and P. Sireesha, *J. Colloid Interface Sci.*, 2017, **504**, 570–578.
- 766 F. Hetsch, X. Xu, H. Wang, S. V. Kershaw and A. L. Rogach, *J. Phys. Chem. Lett.*, 2011, **2**, 1879–1887.
- 767 G. Zhu, T. Xu, T. Lv, L. Pan, Q. Zhao and Z. Sun, *J. Electroanal. Chem.*, 2011, **650**, 248–251.
- 768 Y. Zhu, X. Meng, H. Cui, S. Jia, J. Dong, J. Zheng, J. Zhao, Z. Wang, L. Li, L. Zhang and Z. Zhu, *ACS Appl. Mater. Interfaces*, 2014, **6**, 13833–13840.
- 769 L. Han, N. Koide, Y. Chiba and T. Mitate, *Appl. Phys. Lett.*, 2004, **84**, 2433–2435.
- 770 V. Sudhakar, A. Arulkashmir and K. Krishnamoorthy, *Chem. Commun.*, 2017, **53**, 6629–6632.
- 771 A. Arulkashmir, V. Sudhakar and K. Krishnamoorthy, *Adv. Energy Mater.*, 2016, **6**, 1502334.
- 772 A. A. Madhavan, S. Kalluri, K. D. Chacko, T. A. Arun, S. Nagarajan, K. R. V. Subramanian, A. Sreekumaran Nair, S. V. Nair and A. Balakrishnan, *RSC Adv.*, 2012, **2**, 13032–13037.
- 773 A. Y. Kim, J. Kim, M. Y. Kim, S. W. Ha, N. T. T. Tien and M. Kang, *Bull. Korean Chem. Soc.*, 2012, **33**, 3355–3360.
- 774 L. Chen, Y. Zhou, W. Tu, Z. Li, C. Bao, H. Dai, T. Yu, J. Liu and Z. Zou, *Nanoscale*, 2013, **5**, 3481–3485.
- 775 G. Cheng, M. S. Akhtar, O. B. Yang and F. J. Stadler, *ACS Appl. Mater. Interfaces*, 2013, **5**, 6635–6642.
- 776 W. Shu, Y. Liu, Z. Peng, K. Chen, C. Zhang and W. Chen, *J. Alloys Compd.*, 2013, **563**, 229–233.
- 777 H. Zhang, W. Wang, H. Liu, R. Wang, Y. Chen and Z. Wang, *Mater. Res. Bull.*, 2014, **49**, 126–131.
- 778 S.-B. Kim, J.-Y. Park, C.-S. Kim, K. Okuyama, S.-E. Lee, H.-D. Jang and T.-O. Kim, *J. Phys. Chem. C*, 2015, **119**, 16552–16559.
- 779 Z. Salam, E. Vijayakumar, A. Subramania, N. Sivasankar and S. Mallick, *Sol. Energy Mater. Sol. Cells*, 2015, **143**, 250–259.
- 780 H. Ding, S. Zhang, P.-C. Juan, T.-Y. Liu, Z.-F. Du and D.-L. Zhao, *RSC Adv.*, 2016, **6**, 41092–41102.
- 781 L. Liu, B. Zeng, Q. Meng, Z. Zhang, J. Li, X. Zhang, P. Yang and H. Wang, *Synth. Met.*, 2016, **222**, 219–223.
- 782 L. Liu, Y. Zhang, B. Zhang and Y. Feng, *J. Mater. Sci.*, 2017, **52**, 8070–8083.
- 783 H. Cai, J. Li, X. Xu, H. Tang, J. Luo, K. Binnemans, J. Fransaer and D. E. De Vos, *J. Alloys Compd.*, 2017, **697**, 132–137.
- 784 H. Zhang, Y. Lv, C. Yang, H. Chen and X. Zhou, *J. Electron. Mater.*, 2018, **47**, 1630–1637.
- 785 M. P. Kumar, C. Takahashi, S. Kundu, T. N. Narayanan and D. K. Pattanayak, *New J. Chem.*, 2019, **43**, 14313–14319.
- 786 A. Imbrogno, R. Pandiyan, A. Macario, A. Bonanno and M. A. El Khakani, *IEEE J. Photovolt.*, 2019, **9**, 1240.
- 787 K. S. K. Lo and W. W. F. Leung, *Sol. Energy*, 2019, **180**, 16–24.
- 788 V. S. Manikandan, A. K. Palai, S. Mohanty and S. K. Nayak, *J. Alloys Compd.*, 2019, **793**, 400–409.
- 789 K. Mensah-Darkwa, F. O. Agyemang, D. Yeboah and S. Akromah, *Mater. Today: Proc.*, 2021, **38**, 514.
- 790 K. Basu, G. S. Selopal, M. Mohammadnezad, R. Akilimali, Z. M. Wang, H. Zhao, F. Vetrone and F. Rosei, *Electrochim. Acta*, 2020, **349**, 136409.
- 791 D. Krishnamoorthy and A. Prakasam, *Inorg. Chem. Commun.*, 2020, **118**, 108016.
- 792 Y.-S. Yen, H.-H. Chou, Y.-C. Chen, C.-Y. Hsu and J. T. Lin, *J. Mater. Chem.*, 2012, **22**, 8734–8747.
- 793 J. Wu, Z. Lan, J. Lin, M. Huang, Y. Huang, L. Fan, G. Luo, Y. Lin, Y. Xie and Y. Y. Wei, *Chem. Soc. Rev.*, 2017, **46**, 5975.
- 794 J. E. Trancik, S. C. Barton and J. Hone, *Nano Lett.*, 2008, **8**, 982–987.
- 795 G. Calogero, F. Bonaccorso, O. M. Maragó, P. G. Gucciardi and G. Di Marco, *Dalton Trans.*, 2010, **39**, 2903–2909.
- 796 S. Li, Y. Luo, W. Lv, W. Yu, S. Wu, P. Hou, Q. Yang, Q. Meng, C. Liu and H.-M. Cheng, *Adv. Energy Mater.*, 2011, **1**, 486–490.
- 797 L. Kavan, J.-H. Yum and M. Grätzel, *Nano Lett.*, 2011, **11**, 5501–5506.
- 798 L. Kavan, J.-H. Yum, M. K. Nazeeruddin and M. Grätzel, *ACS Nano*, 2011, **5**, 9171–9178.
- 799 J. Baker, D. Deganello, D. T. Gethin and T. M. Watson, *Mater. Res. Innovations*, 2014, **18**, 86–90.
- 800 J. Velten, A. J. Mozer, D. Li, D. Officer, G. Wallace, R. Baughman and A. Zakhidov, *Nanotechnology*, 2012, **23**, 085201.
- 801 H. Kim, H. Choi, S. Hwang, Y. Kim and M. Jeon, *Nano-scale Res. Lett.*, 2012, **7**, 53.
- 802 M. J. Ju, J. C. Kim, H.-J. Choi, I. T. Choi, S. G. Kim, K. Lim, J. Ko, J.-J. Lee, I.-Y. Jeon, J.-B. Baek and H. K. Kim, *ACS Nano*, 2013, **7**, 5243–5250.



- 803 Z. Wen, S. Cui, H. Pu, S. Mao, K. Yu and X. Feng, *Adv. Mater.*, 2011, **23**, 5445–5450.
- 804 H. Yamaguchi, G. Eda, C. Mattevi, H. Kim and M. Chhowalla, *ACS Nano*, 2010, **4**, 524–528.
- 805 Z.-S. Wu, S. Pei, W. Ren, D. Tang, L. Gao, B. Liu, F. Li, C. Liu and H.-M. Cheng, *Adv. Mater.*, 2009, **21**, 1756–1760.
- 806 W. Hong, Y. Xu, G. Lu, C. Li and G. Shi, *Electrochem. Commun.*, 2008, **10**, 1555–1558.
- 807 Z. Yang, M. Liu, C. Zhang, W. W. Tjiu, T. Liu and H. Peng, *Angew. Chem., Int. Ed.*, 2013, **52**, 3996–3999.
- 808 Y. Jo, J. Y. Cheon, J. Yu, H. Y. Jeong, C.-H. Han, Y. Jun and S. H. Joo, *Chem. Commun.*, 2012, **48**, 8057–8059.
- 809 N. Papageorgiou, W. F. Maier and M. Grätzel, *J. Electrochem. Soc.*, 1997, **144**, 876.
- 810 B. K. Koo, D. Y. Lee, H. J. Kim, W. J. Lee, J. S. Song and H. J. Kim, *J. Electroceram.*, 2006, **17**, 79–82.
- 811 G. Tsekouras, A. J. Mozer and G. G. Wallace, *J. Electrochem. Soc.*, 2008, **155**, K124–K128.
- 812 A. Kaniyoor and S. Ramaprabhu, *J. Appl. Phys.*, 2011, **109**, 124308.
- 813 S. Gagliardi, L. Giorgi, R. Giorgi, N. Lisi, T. D. Makris, E. Salernitano and A. Ruffoloni, *Superlattices Microstruct.*, 2009, **46**, 205–208.
- 814 M. Y. Yen, C. C. Teng, M. C. Hsiao, P. I. Liu, W. P. Chung, C. C. M. Ma, C. K. Hsieh, M. C. Tsai and C. H. Tsai, *J. Mater. Chem.*, 2011, **21**, 12880–12888.
- 815 C. Xu, X. Wang and J. Zhu, *J. Phys. Chem. C*, 2008, **112**, 19841–19845.
- 816 K. Lim, C. Kim, J. Song, T. Yu, W. Lim, K. Song, P. Wang, N. Zu and J. Ko, *J. Phys. Chem. C*, 2011, **115**, 22640–22646.
- 817 D. S. Su, J. Zhang, B. Frank, A. Thomas, X. Wang, J. Paraknowitsch and R. Schlogl, *ChemSusChem*, 2010, **3**, 169–180.
- 818 D. S. Yu, E. Nagelli, F. Du and L. Dai, *J. Phys. Chem. Lett.*, 2010, **1**, 2165–2173.
- 819 H. Choi, H. Kim, S. Hwang, Y. Han and M. Jeon, *J. Mater. Chem.*, 2011, **21**, 7548–7551.
- 820 V. Tjoa, J. Chua, S. S. Pramana, J. Wei, S. G. Mhaisalkar and N. Mathews, *ACS Appl. Mater. Interfaces*, 2012, **4**, 3447–3452.
- 821 M.-S. Wu and Y.-J. Zheng, *Phys. Chem. Chem. Phys.*, 2013, **15**, 1782–1787.
- 822 L. Chen, C. X. Guo, Q. Zhang, Y. Lei, J. Xie, S. Ee, G. Guai, Q. Song and C. M. Li, *ACS Appl. Mater. Interfaces*, 2013, **5**, 2047–2052.
- 823 P. Zhai, C.-C. Lee, Y.-H. Chang, C. Liu, T.-C. Wei and S.-P. Feng, *ACS Appl. Mater. Interfaces*, 2015, **7**, 2116–2123.
- 824 J. Gong, Z. Zhou, K. Sumathy, H. Yang and Q. Qiao, *J. Appl. Phys.*, 2016, **119**, 135501.
- 825 L. Kavan, H. Krysova, P. Janda, H. Tarabkova, Y. Saygili, M. Freitag, S. M. Zakeeruddin, A. Hagfeldt and M. Grätzel, *Electrochim. Acta*, 2017, **251**, 167–175.
- 826 J. Ma, S. Yuan, S. Yang, H. Lu and Y. Li, *Appl. Surf. Sci.*, 2018, **440**, 8–15.
- 827 B. Tang, H. Yu, W. Huang, Y. Sun, X. Li, S. Li and T. Ma, *RSC Adv.*, 2019, **9**, 15678–15685.
- 828 D. Torres, D. Sebastián, M. J. Lázaro, J. L. Pinilla, I. Suelves, A. S. Aricò and V. Baglio, *Electrochim. Acta*, 2019, **306**, 396–406.
- 829 D. K. Kumar, S. K. Swami, V. Dutta, B. Chen, N. Bennett and H. M. Upadhyaya, *FlatChem*, 2019, **15**, 100105.
- 830 K. Kakiage, Y. Aoyama, T. Yano, K. Oya, J. I. Fujisawa and M. Hanaya, *Chem. Commun.*, 2015, **51**, 15894–15897.
- 831 S. Mathew, A. Yella, P. Gao, R. Humphry-Baker, B. F. Curchod, N. Ashari-Astani, I. Tavernelli, U. Rothlisberger, M. K. Nazeeruddin and M. Grätzel, *Nat. Chem.*, 2014, **6**, 242–247.
- 832 E. Singh, K. S. Kim, G. Y. Yeom and H. S. Nalwa, *RSC Adv.*, 2017, **7**, 28234–28249.
- 833 S. Rashidi, S. Rashidi, R. K. Heydari, S. Esmaeili, N. Tran, D. Thangi and W. Wei, *Prog. Photovolt.: Res. Appl.*, 2021, **29**, 238–261.
- 834 M. Wu, Y. Wang, X. Lin, N. Yu, L. Wang, L. Wang, A. Hagfeldt and T. Ma, *Phys. Chem. Chem. Phys.*, 2011, **13**, 19298–19301.
- 835 F. S. Freitas, A. S. Gonçalves, A. de Moraes, J. E. Benedetti and A. F. Nogueira, *NanoGe J. Energy Sustainable*, 2013, **1**, 011002.
- 836 M. Al-Mamun, H. Zhang, P. Liu, Y. Wang, J. Cao and H. Zhao, *RSC Adv.*, 2014, **4**, 21277–21283.
- 837 W. Liu, S. He, Y. Wang, Y. Dou, D. Pan, Y. Feng, G. Qian, J. Xu and S. Miao, *Electrochim. Acta*, 2014, **144**, 119–126.
- 838 G. Yue, X. Ma, Q. Jianga, F. Tana, J. Wub, C. Chena, F. Li and Q. Li, *Electrochim. Acta*, 2014, **142**, 68–75.
- 839 S.-S. Kim, J. Won Lee, J.-M. Yun and S.-I. Na, *J. Ind. Eng. Chem.*, 2015, **29**, 71–74.
- 840 S. H. Ahn and A. Manthiram, *Adv. Energy Mater.*, 2016, **6**, 1501814.
- 841 D. Vikraman, S. A. Patil, S. Hussain, N. Mengal, H.-S. Kim, S. H. Jeong, J. Jung, H.-S. Kim and H. J. Park, *Dyes Pigm.*, 2018, **151**, 7–14.
- 842 A. J. Bard and L. R. Faulkner, *Electrochemical Methods: Fundamentals and Applications*, Wiley, New York, 2001.
- 843 D. Vikraman, S. Hussain, S. A. Patil, L. Truong, A. A. Arbab, S. H. Jeong, S. H. Chun, J. Jung and H. S. Kim, *ACS Appl. Mater. Interfaces*, 2021, **13**, 5061–5072.
- 844 J.-Y. Lin, C.-Yi Chan and S.-W. Chou, *Chem. Commun.*, 2013, **49**, 1440–1442.
- 845 G. Yue, J. Y. Lin, S. Y. Tai, Y. Xiao and J. Wu, *Electrochim. Acta*, 2012, **85**, 162–168.
- 846 Y. Wang, S. Li, Y. Bai, Z. Chen, Q. Jiang, T. Li and W. Zhang, *Electrochim. Acta*, 2013, **114**, 30–34.
- 847 J. Guo, Y. Shi, C. Zhu, L. Wang, N. Wang and T. Ma, *J. Mater. Chem. A*, 2013, **1**, 11874–11879.
- 848 M. A. Ibrahim, W. C. Huang, T. W. Lan, K. M. Boopathi, Y. C. Hsiao, C. H. Chen, W. Budiawan, Y. Y. Chen, C. S. Chang, L. J. Li, C. H. Tsai and C. C. Chu, *J. Mater. Chem. A*, 2014, **2**, 11382–11390.
- 849 W. Liu, S. He, T. Yang, Y. Feng, G. Qian, J. Xu and S. Miao, *Appl. Surf. Sci.*, 2014, **313**, 498–503.
- 850 B. Lei, G. R. Li and X. P. Gao, *J. Mater. Chem. A*, 2014, **2**, 3919–3925.



- 851 S. A. Patil, P. Y. Kalode, R. S. Mane, D. V. Shinde, A. Doyoung, C. Keumnam, M. M. Sung, S. B. Ambade and S. H. Han, *Dalton Trans.*, 2014, **43**, 5256–5259.
- 852 I. A. Ji, H. M. Choi and J. H. Bang, *Mater. Lett.*, 2014, **123**, 51–54.
- 853 J. Guo, S. Liang, Y. Shi, C. Hao, X. Wang and T. Ma, *Phys. Chem. Chem. Phys.*, 2015, **17**, 28985–28992.
- 854 C. H. Lin, C. H. Tsai, F. G. Tseng, Y. Y. Yu, H. C. Wu and C. K. Hsieh, *Nanoscale Res. Lett.*, 2015, **10**, 446.
- 855 W. Wei, K. Sun and Y. H. Hu, *J. Mater. Chem. A*, 2016, **4**, 12398–12401.
- 856 H. Jeong, J. Y. Kim, B. Koo, H. J. Son, D. Kim and M. J. Ko, *J. Power Sources*, 2016, **330**, 104–110.
- 857 J. Liang, J. Li, H. Zhu, Y. Han, Y. Wang, C. Wang, Z. Jin, G. Zhang and J. Liu, *Nanoscale*, 2016, **8**, 16017–16025.
- 858 C. Tan, W. Zhao, A. Chaturvedi, Z. Fei, Z. Zeng, J. Chen, Y. Huang, P. Ercius, Z. Luo, X. Qi and B. Chen, *Small*, 2016, **12**, 1866–1874.
- 859 X. Meng, C. Yu, B. Lu, J. Yang and J. Qiu, *Nano Energy*, 2016, **22**, 59–69.
- 860 N. Huang, G. Li, Z. Xia, F. Zheng, H. Huang, W. Li, C. Xiang, Y. Sun, P. Sun and X. Sun, *Electrochim. Acta*, 2017, **235**, 182–190.
- 861 V. H. V. Quy, E. Vijayakumar, P. Ho, J.-H. Park, J. A. Rajesh, J. Kwon, J. Chae, J.-H. Kim, S.-H. Kang and K.-S. Ahn, *Electrochim. Acta*, 2018, **260**, 716–725.
- 862 D. Vikraman, S. A. Patil, S. Hussain, N. Mengal, H.-S. Kim, S. H. Jeong, J. Jung, H.-S. Kim and H. J. Park, *Dyes Pigm.*, 2018, **151**, 7–14.
- 863 S. Vijaya, G. Landi, J. J. Wu and S. Anandan, *Electrochim. Acta*, 2019, **294**, 134–141.
- 864 C.-J. Liu, S.-Y. Tai, S.-W. Chou, Y.-C. Yu, K.-D. Chang, S. Wang, F. S.-S. Chien, J.-Y. Lin and T.-W. Lin, *J. Mater. Chem.*, 2012, **22**, 21057–21064.
- 865 Z. Li, F. Gong, G. Zhou and Z. S. Wang, *J. Phys. Chem. C*, 2013, **117**, 6561–6566.
- 866 V.-D. Dao, L. L. Larina, K.-D. Jung, J.-K. Lee and H.-S. Choi, *Nanoscale*, 2014, **6**, 477–482.
- 867 J. Shen, R. Cheng, Y. Luo, Y. Chen, X. Chen, Z. Sun and S. Huang, *J. Solid State Electrochem.*, 2015, **19**, 1045–1052.
- 868 L. Zhou, J. Luo, X. Yang, B. Yang, X. Zuo, H. Tang, H. Zhang and G. Li, *Funct. Mater. Lett.*, 2015, **8**, 1550011.
- 869 J. Huo, J. Wu, M. Zheng, Y. Tu and Z. Lan, *J. Power Sources*, 2015, **293**, 570–576.
- 870 S. Jiang, X. Yin, J. Zhang, X. Zhu, J. Li and M. He, *Nanoscale*, 2015, **7**, 10459–10464.
- 871 Z. Shen, M. Wang, L. Liu, M. V. Sofianos, H. Yang, S. Wang and S. Liu, *Electrochim. Acta*, 2018, **266**, 130–138.
- 872 K. Zhang, J. Yao, X. Zuo, Q. Yang, H. Tang, G. Li, M. Wu, K. Zhu and H. Zhang, *CrystEngComm*, 2018, **20**, 1252–1263.
- 873 D. Vikraman, A. A. Arbab, S. Hussain, N. K. Shrestha, S. H. Jeong, J. Jung, S. A. Patil and H. S. Kim, *ACS Sustainable Chem. Eng.*, 2019, **7**, 13195–13205.
- 874 U. Mehmood, H. Asghar, F. Babar and M. Younas, *Sol. Energy*, 2020, **196**, 132–136.
- 875 K. Silambarasan, J. Archana, S. Athithya, S. Harish, R. S. Ganesh, M. Navaneethan, S. Ponnusamy, C. Muthamizhchelvan, K. Hara and Y. Hayakawa, *Appl. Surf. Sci.*, 2020, **501**, 144010.
- 876 R. S. Ganesh, E. Durgadevi, K. Silambarasan, M. Navaneethan, S. Ponnusamy, C. Y. Kong, C. Muthamizhchelvan, Y. Shimura and Y. Hayakawa, *Mater. Sci. Semicond. Process.*, 2020, **105**, 104725.
- 877 G. Li, X. Chen and G. Gao, *Nanoscale*, 2014, **6**, 3283–3288.
- 878 V. Murugadoss, J. Lin, H. Liu, X. Mai, T. Ding, Z. Guo and S. Angaiah, *Nanoscale*, 2019, **11**, 17579.
- 879 S. Yoon, S. Tak, J. Kim, Y. Jun, K. Kang and J. Park, *Build. Environ.*, 2011, **46**, 1899–1904.
- 880 T. Xu, P. Wei, X. Ren, H. Liu, L. Chen, W. Tian, S. Liu and Z. Guo, *Mater. Lett.*, 2017, **195**, 100–103.
- 881 A. Gurung, H. Elbohy, D. Khatiwada, A. F. Mitul and Q. Qiao, *IEEE J. Photovolt.*, 2016, **6**, 912–917.
- 882 Y. Duan, Q. Tang, J. Liu, B. He and L. Yu, *Angew. Chem., Int. Ed.*, 2014, **53**, 14569–14574.
- 883 R. Chen, K. Sun, Q. Zhang, Y. Zhou, M. Li, Y. Sun, Z. Wu, Y. Wu, X. Li, J. Xi, C. Ma, Y. Zhang and J. Ouyang, *iScience*, 2019, **12**, 66–75.
- 884 P.-Y. Chen, C.-T. Li, C.-P. Lee, R. Vittal and K.-C. Ho, *Nano Energy*, 2015, **12**, 374–385.
- 885 J. Xia, Q. Wang, Q. Xu, R. Yu, L. Chen, J. Jiao, S. Fan and H. Wu, *Appl. Surf. Sci.*, 2020, **530**, 147238.
- 886 T. Xu, D. Kong, H. Tang, X. Qin, X. Li, A. Gurung, K. Kou, L. Chen, Q. Qiao and W. Huang, *ACS Omega*, 2020, **5**, 8687–8696.
- 887 <https://www.grandviewresearch.com/industry-analysis/dye-sensitized-solar-cell-market> (accessed on June 2021).
- 888 M. Freitag, J. Teuscher, Y. Saygili, X. Zhang, F. Giordano, P. Liska, J. Hua, S. M. Zakeeruddin, J.-E. Moser, M. Grätzel and A. Hagfeldt, *Nat. Photonics*, 2017, **11**, 372–378.
- 889 Y. M. Cao, Y. H. Liu, S. M. Zakeeruddin, A. Hagfeldt and M. Gratzel, *Joule*, 2018, **2**, 1108–1117.
- 890 G. Boschloo, *Front. Chem.*, 2019, **7**, 77.
- 891 Y. Chiba, A. Islam, Y. Watanabe, R. Komiya, N. Koide and L. Han, *Jpn. J. Appl. Phys.*, 2006, **45**, L638.
- 892 M. K. Nazeeruddin, P. Pechy, T. Renouard, S. M. Zakeeruddin, R. Humphry-Baker, P. Comte, P. Liska, L. Cevey, E. Costa, V. Shklover and L. Spiccia, *J. Am. Chem. Soc.*, 2001, **123**, 1613–1624.
- 893 A. Fakhruddin, R. Jose, T. M. Brown, F. Fabregat-Santiago and J. Bisquert, *Energy Environ. Sci.*, 2014, **7**, 3952–3981.
- 894 G. Gorni, I. Zama, C. Martelli and L. Armiento, *J. Eur. Ceram. Soc.*, 2019, **39**, 85–91.
- 895 A. Kojima, K. Teshima, Y. Shirai and T. Miyasaka, *J. Am. Chem. Soc.*, 2009, **131**, 6050.
- 896 T. A. Berhe, W.-N. Su, C.-H. Chen, C.-J. Pan, J.-H. Cheng, H.-M. Chen, M.-C. Tsai, L.-Y. Chen, A. A. Dubale and B.-J. Hwang, *Energy Environ. Sci.*, 2016, **9**, 323.
- 897 N. Ali, A. Hussain, R. Ahmed, M. K. Wang, C. Zhao, B. U. Haq and Y. Q. Fu, *Renewable Sustainable Energy Rev.*, 2016, **59**, 726.



- 898 <https://www.nrel.gov/pv/cell-efficiency.html> (accessed on June 2021).
- 899 I. Borriello, G. Cantele and D. Ninno, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2008, **77**, 235214.
- 900 M. A. Peña and J. L. G. Fierro, *Chem. Rev.*, 2001, **101**, 1981–2018.
- 901 M. L. Parisi, S. Maranghi, L. Vesce, A. Sinicropi, A. Di Carlo and R. Basosi, *Renewable Sustainable Energy Rev.*, 2020, **121**, 109703.
- 902 F. Brivio, J. M. Frost, J. M. Skelton, A. J. Jackson, O. J. Weber, M. T. Weller, A. R. Goni, A. M. A. Leguy, P. R. F. Barnes and A. Walsh, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2015, **92**, 144308.
- 903 M. Saliba, T. Matsui, K. Domanski, J.-Y. Seo, A. Ummadisingu, S. M. Zakeeruddin, J.-P. Correa-Baena, W. R. Tress, A. Abate, A. Hagfeldt and M. Grätzel, *Science*, 2016, **354**, 206.
- 904 N. G. Park, *Mater. Today*, 2015, **18**, 65–72.
- 905 M. A. Green, A. Ho-Baillie and H. J. Snaith, *Nat. Photonics*, 2014, **8**, 506–514.
- 906 M. M. Lee, J. Teuscher, T. Miyasaka, T. N. Murakami and H. J. Snaith, *Science*, 2012, **338**, 643.
- 907 H.-S. Kim, C.-R. Lee, J.-H. Im, K.-B. Lee, T. Moehl, A. Marchioro, S.-J. Moon, R. Humphry-Baker, J.-H. Yum, J. E. Moser, M. Grätzel and N.-G. Park, *Sci. Rep.*, 2012, **2**, 591.
- 908 B.-E. Cohen and L. Etgar, *Front. Optoelectron.*, 2016, **9**, 44–52.
- 909 T. C. Sum and N. Mathews, *Energy Environ. Sci.*, 2014, **7**, 2518–2534.
- 910 Z. Song, S. C. Watthage, A. B. Phillips and M. J. Heben, *J. Photonics Energy*, 2016, **6**, 22001.
- 911 H. S. Jung and N. G. Park, *Small*, 2015, **11**, 10–25.
- 912 G. Xing, N. Mathews, S. Sun, S. S. Lim, Y. M. Lam, M. Gratzel, S. Mhaisalkar and T. C. Sum, *Science*, 2013, **342**, 344–347.
- 913 S. D. Stranks, G. E. Eperon, G. Grancini, C. Menelaou, M. J. P. Alcocer, T. Leijtens, L. M. Herz, A. Petrozza and H. J. Snaith, *Science*, 2014, **342**, 341–344.
- 914 J. M. Ball, M. M. Lee, A. Hey and H. J. Snaith, *Energy Environ. Sci.*, 2013, **6**, 1739.
- 915 T. Salim, S. Sun, Y. Abe, A. Krishna, A. C. Grimsdale and Y. M. Lam, *J. Mater. Chem. A*, 2015, **3**, 8943–8969.
- 916 A. K. Jena, A. Kulkarni and T. Miyasaka, *Chem. Rev.*, 2019, **119**, 3036–3103.
- 917 K. Mahmood, B. S. Swain and A. Amassian, *Adv. Energy Mater.*, 2015, **5**, 1500568.
- 918 P. Zhang, J. Wu, T. Zhang, Y. Wang, D. Liu, H. Chen, L. Ji, C. Liu, W. Ahmad, Z. D. Chen and S. Li, *Adv. Mater.*, 2018, **30**, 1703737.
- 919 P. J. Cameron and L. M. Peter, *J. Phys. Chem. B*, 2003, **107**, 14394–14400.
- 920 L. Kavan, M. Zukalova, O. Vik and D. Havlicek, *ChemPhysChem*, 2014, **15**, 1056–1061.
- 921 S. M. Waita, B. O. Aduda, J. M. Mwabara, G. A. Niklasson, C. G. Granqvist and G. Boschloo, *J. Electroanal. Chem.*, 2009, **637**, 79–83.
- 922 Q. Q. Liu, D. W. Zhang, J. Shen, Z. Q. Li, J. H. Shi, Y. W. Chen, Z. Sun, Z. Yang and S. M. Huang, *Surf. Coat. Technol.*, 2013, **231**, 126.
- 923 S. Y. Lin, T. S. Su, T. Y. Hsieh, P. C. Lo and T. C. Wei, *Adv. Energy Mater.*, 2017, **7**, 1700169.
- 924 T. S. Su, T. Y. Hsieh, C. Y. Hong and T. C. Wei, *Sci. Rep.*, 2015, **5**, 16098.
- 925 M. Manca, F. Malara, L. Martiradonna, L. De Marco, R. Giannuzzi, R. Cingolani and G. Gigli, *Thin Solid Films*, 2010, **518**, 7147–7151.
- 926 H. Zhang, H. Wang, M. Ma, Y. Wu, S. Dong and Q. Xu, *Sol. RRL*, 2018, **2**, 1800097.
- 927 J. Lungu, G. Socol, G. E. Stan, N. Ștefan, C. Luculescu, A. Georgescu, G. Popescu-Pelin, G. Prodan, M. A. Gîrțu and I. N. Mihăilescu, *Nanomaterials*, 2019, **9**, 746.
- 928 A. Priyadarshi, A. Bashir, J. T. Gunawan, L. J. Haur, A. Bruno, Z. Akhter, N. Mathews and S. G. Mhaisalkar, *Energy Technol.*, 2017, **5**, 1866–1872.
- 929 M. Che, L. Zhu, Y. L. Zhao, D. S. Yao, X. Q. Gu, J. Song and Y. H. Qiang, *Mater. Sci. Semicond. Process.*, 2016, **56**, 29–36.
- 930 A. J. Pearson, G. E. Eperon, P. E. Hopkinson, S. N. Habisreutinger, J. T. W. Wang, H. J. Snaith and N. C. Greenham, *Adv. Energy Mater.*, 2016, **6**, 1600014.
- 931 X. Yu, S. Chen, K. Yan, X. Cai, H. Hu, M. Peng, B. Chen, B. Dong, X. Gao and D. Zou, *J. Power Sources*, 2016, **325**, 534–540.
- 932 N. Cheng, P. Liu, S. Bai, Z. Yu, W. Liu, S. S. Guo and X. Z. Zhao, *J. Power Sources*, 2016, **321**, 71–75.
- 933 D. M. Antonelli and J. Y. Ying, *Angew. Chem., Int. Ed. Engl.*, 1995, **34**, 2014–2017.
- 934 M. A. Khan, M. S. Akhtar and O. B. Yang, *Sol. Energy*, 2010, **84**, 2195–2201.
- 935 Y. Saito, S. Kambe, T. Kitamura, Y. Wada and S. Yanagida, *Sol. Energy Mater. Sol. Cells*, 2004, **83**, 1–13.
- 936 Q. Li, X. Zou, Y. Li, Y. Pei, S. Zeng and D. Guo, *Int. J. Photoenergy*, 2017, **2017**, 8107073.
- 937 B. Taheri, N. Y. Nia, A. Agresti, S. Pescetelli, C. Ciceroni, A. E. Del Rio Castillo, L. Cinà, S. Bellani, F. Bonaccorso and A. Di Carlo, *2D Mater.*, 2018, **5**, 045034.
- 938 M. C. Kim, B. J. Kim, J. Yoon, J. W. Lee, D. Suh, N. G. Park, M. Choi and H. S. Jung, *Nanoscale*, 2015, **7**, 20725–20733.
- 939 D. Burkitt, J. Searle and T. Watson, *R. Soc. Open Sci.*, 2018, **5**, 172158.
- 940 N. Li, L. Song, L. Bießmann, S. Xia, W. Ohm, C. J. Brett, E. Hadjixenophontos, G. Schmitz, S. V. Roth and P. Müller-Buschbaum, *Adv. Mater. Interfaces*, 2019, **6**, 1900558.
- 941 A. J. Huckaba, Y. Lee, R. Xia, S. Paek, V. C. Bassetto, E. Oveis, A. Lesch, S. Kinge, P. J. Dyson, H. Girault and M. K. Nazeeruddin, *Energy Technol.*, 2019, **7**, 317–324.
- 942 L. Passoni, F. Fumagalli, A. Perego, S. Bellani, P. Mazzolini and F. Di Fonzo, *Nanotechnology*, 2017, **28**, 245603.
- 943 A. Ghadirzadeh, F. Fumagalli, A. Mezzetti, S. Bellani, L. Meda, M. R. Antognazza and F. Di Fonzo, *ChemPhotoChem*, 2018, **2**, 283–292.



- 944 C. J. Barbé, F. Arendse, P. Comte, M. Jirousek, F. Lenzmann, V. Shklover and M. Grätzel, *J. Am. Ceram. Soc.*, 2015, **80**, 3157–3171.
- 945 S. Uchida, M. Tomiha, H. Takizawa and M. Kawayaya, *J. Photochem. Photobiol., A*, 2004, **164**, 93–96.
- 946 G. Mincuzzi, L. Vesce, A. Reale, A. Di Carlo and T. M. Brown, *Appl. Phys. Lett.*, 2009, **95**, 103312.
- 947 S. P. Malyukov and A. V. Sayenko, *J. Russ. Laser Res.*, 2013, **34**, 531–536.
- 948 H.-J. Hwang and H.-S. Kim, *J. Nanosci. Nanotechnol.*, 2015, **15**, 5028–5034.
- 949 T. Watson, I. Mabbett, H. Wang, L. Peter and D. Worsley, *Prog. Photovolt.: Res. Appl.*, 2011, **19**, 482–486.
- 950 K. Hooper, M. Carnie, C. Charbonneau and T. Watson, *Int. J. Photoenergy*, 2014, **2014**, 953623.
- 951 H. Hu, M. Singh, T. Wan, J. Tang, C. W. Chu and G. Li, *J. Mater. Chem. A*, 2020, **8**, 1578–1603.
- 952 L. Tzounis, T. Stergiopoulos, A. Zachariadis, C. Gravalidis, A. Laskarakis and S. Logothetidis, *Mater. Today: Proc.*, 2017, **4**, 5082–5089.
- 953 M. K. Kim, H. S. Lee, S. R. Pae, D. J. Kim, J. Y. Lee, I. Gereige, S. Park and B. Shin, *J. Mater. Chem. A*, 2018, **6**, 24911–24919.
- 954 F. Xu, T. Zhang, G. Li and Y. Zhao, *J. Mater. Chem. A*, 2017, **5**, 11450–11461.
- 955 D.-Y. Son, S.-G. Kim, J.-Y. Seo, S.-H. Lee, H. Shin, D. Lee and N.-G. Park, *J. Am. Chem. Soc.*, 2018, **140**, 1358–1364.
- 956 J. G. Tait, S. Manghooli, W. Qiu, L. Rakocevic, L. Kootstra, M. Jaysankar, C. A. Masse de la Huerta, U. W. Paetzold, R. Gehlhaar, D. Cheyins, P. Heremans and J. Poortmans, *J. Mater. Chem. A*, 2016, **4**, 3792–3797.
- 957 S. Das, B. Yang, G. Gu, P. C. Joshi, I. N. Ivanov, C. M. Rouleau, T. Aytug, D. B. Geohegan and K. Xiao, *ACS Photonics*, 2015, **2**, 680–686.
- 958 J. H. Heo, M. H. Lee, M. H. Jang and S. H. Im, *J. Mater. Chem. A*, 2016, **4**, 17636–17642.
- 959 J. E. Bishop, T. J. Routledge and D. G. Lidzey, *J. Phys. Chem. Lett.*, 2018, **9**, 1977–1984.
- 960 J. Ávila, C. Momblona, P. P. Boix, M. Sessolo and H. J. Bolink, *Joule*, 2017, **1**, 431–442.
- 961 L. K. Ono, M. R. Leyden, S. Wang and Y. Qi, *J. Mater. Chem. A*, 2016, **4**, 6693–6713.
- 962 L. Gil-Escrig, C. Momblona, M. G. La-Placa, P. P. Boix, M. Sessolo and H. J. Bolink, *Adv. Energy Mater.*, 2018, **8**, 1703506.
- 963 R. Singh, I. M. Noor, P. K. Singh, B. Bhattacharya and A. K. Arof, *J. Mol. Struct.*, 2018, **1158**, 229–233.
- 964 Y. Galagan, F. Di Giacomo, H. Gorter, G. Kirchner, I. de Vries, R. Andriessen and P. Groen, *Adv. Energy Mater.*, 2018, **8**, 1801935.
- 965 S. M. Park, Y. J. Noh, S. H. Jin and S. I. Na, *Sol. Energy Mater. Sol. Cells*, 2016, **155**, 14–19.
- 966 Y. Ju, S. Y. Park, K. M. Yeom, J. H. Noh and H. S. Jung, *ACS Appl. Mater. Interfaces*, 2019, **11**, 11537–11544.
- 967 E. H. Jung, N. J. Jeon, E. Y. Park, C. S. Moon, T. J. Shin, T.-Y. Yang, J. H. Noh and J. Seo, *Nature*, 2019, **567**, 511.
- 968 J. Xiao, J. Shi, H. Liu, Y. Xu, S. Lv, Y. Luo, D. Li, Q. Meng and Y. Li, *Adv. Energy Mater.*, 2015, **5**, 1401943.
- 969 H. A. Abbas, R. Kottokkaran, B. Ganapathy, M. Samiee, L. Zhang, A. Kitahara, M. Noack and V. L. Dalal, *APL Mater.*, 2015, **3**, 016105.
- 970 D. Bi, C. Yi, J. Luo, J.-D. Décoppet, F. Zhang, S. M. Zakeeruddin, X. Li, A. Hagfeldt and M. Grätzel, *Nat. Energy*, 2016, **1**, 16142.
- 971 J. Feng, X. Zhu, Z. Yang, X. Zhang, J. Niu, Z. Wang, S. Zuo, S. Priya, S. Liu and D. Yang, *Adv. Mater.*, 2018, **30**, 1801418.
- 972 W. S. Yang, B.-W. Park, E. H. Jung, N. J. Jeon, Y. C. Kim, D. U. Lee, S. S. Shin, J. Seo, E. K. Kim and J. H. Noh, *Science*, 2017, **356**, 1376.
- 973 X. Jiang, Z. Yu, Y. Zhang, J. Lai, J. Li, G. G. Gurzadyan, X. Yang and L. Sun, *Sci. Rep.*, 2017, **7**, 42564.
- 974 S. Chavhan, O. Miguel, H.-J. Grande, V. Gonzalez-Pedro, R. S. Sánchez, E. M. Barea, I. Mora-Seró and R. Tena-Zaera, *J. Mater. Chem. A*, 2014, **2**, 12754.
- 975 P. Qin, S. Tanaka, S. Ito, N. Tetreault, K. Manabe, H. Nishino, M. K. Nazeeruddin and M. Grätzel, *Nat. Commun.*, 2014, **5**, 3834.
- 976 B. Pashaei, H. Shahroosvand, S. Bellani and F. Bonaccorso, *Chem. Sci.*, 2020, **11**, 2429–2439.
- 977 K. Do, H. Choi, K. Lim, H. Jo, J. W. Cho, M. K. Nazeeruddin and J. Ko, *Chem. Commun.*, 2014, **50**, 10971.
- 978 G. Xing, N. Mathews, S. Sun, S. S. Lim, Y. M. Lam, M. Grätzel, S. Mhaisalkar and T. C. Sum, *Science*, 2013, **342**, 344–347.
- 979 Z. L. Tseng, C. H. Chiang and C. G. Wu, *Sci. Rep.*, 2015, **5**, 13211.
- 980 D. Liu and T. L. Kelly, *Nat. Photonics*, 2014, **8**, 133–138.
- 981 J. Kim, G. Kim, T. K. Kim, S. Kwon, H. Back, J. Lee, S. H. Lee, H. Kang and K. Lee, *J. Mater. Chem. A*, 2014, **2**, 17291–17296.
- 982 Q. Jiang, Z. Chu, P. Wang, X. Yang, H. Liu, Y. Wang, Z. Yin, J. Wu, X. Zhang and J. You, *Adv. Mater.*, 2017, **29**, 1703852.
- 983 Y. W. Noh, J. H. Lee, I. S. Jin, S. H. Park and J. W. Jung, *Nano Energy*, 2019, **65**, 104014.
- 984 X. Ren, D. Yang, Z. Yang, J. Feng, X. Zhu, J. Niu, Y. Liu, W. Zhao and S. F. Liu, *ACS Appl. Mater. Interfaces*, 2017, **9**, 2421–2429.
- 985 D. Yang, R. Yang, K. Wang, C. Wu, X. Zhu, J. Feng, X. Ren, G. Fang, S. Priya and S. F. Liu, *Nat. Commun.*, 2018, **9**, 1–11.
- 986 Q. Jiang, X. Zhang and J. You, *Small*, 2018, **14**, 1801154.
- 987 M. I. H. Ansari, A. Qurashi and M. K. Nazeeruddin, *J. Photochem. Photobiol., C*, 2018, **35**, 1–24.
- 988 S. Gamliel and L. Etgar, *RSC Adv.*, 2014, **4**, 29012–29021.
- 989 Z. Zhu, Y. Bai, T. Zhang, Z. Liu, X. Long, Z. Wei, Z. Wang, L. Zhang, J. Wang, F. Yan and S. Yang, *Angew. Chem.*, 2014, **126**, 12779–12783.
- 990 L. Hu, J. Peng, W. Wang, Z. Xia, J. Yuan, J. Lu, X. Huang, W. Ma, H. Song, W. Chen and Y. B. Cheng, *ACS Photonics*, 2014, **1**, 547–553.



- 991 X. Yin, Z. Yao, Q. Luo, X. Dai, Y. Zhou, Y. Zhang, Y. Zhou, S. Luo, J. Li, N. Wang and H. Lin, *ACS Appl. Mater. Interfaces*, 2017, **9**, 2439–2448.
- 992 D. Liu, Y. Li, J. Yuan, Q. Hong, G. Shi, D. Yuan, J. Wei, C. Huang, J. Tang and M. K. Fung, *J. Mater. Chem. A*, 2017, **5**, 5701–5708.
- 993 D. Huang, T. Goh, J. Kong, Y. Zheng, S. Zhao, Z. Xu and A. D. Taylor, *Nanoscale*, 2017, **9**, 4236–4243.
- 994 K. Zhao, R. Munir, B. Yan, Y. Yang, T. Kim and A. Amassian, *J. Mater. Chem. A*, 2015, **3**, 20554–20559.
- 995 W. Y. Chen, L. L. Deng, S. M. Dai, X. Wang, C. B. Tian, X. X. Zhan, S. Y. Xie, R. B. Huang and L. S. Zheng, *J. Mater. Chem. A*, 2015, **3**, 19353–19359.
- 996 C. Zuo and L. Ding, *Small*, 2015, **11**, 5528–5532.
- 997 S. Chatterjee and A. J. Pal, *J. Phys. Chem. C*, 2016, **120**, 1428–1437.
- 998 H. Peng, W. Sun, Y. Li, S. Ye, H. Rao, W. Yan, H. Zhou, Z. Bian and C. Huang, *Nano Res.*, 2016, **9**, 2960–2971.
- 999 Y. Bai, H. Yu, Z. Zhu, K. Jiang, T. Zhang, N. Zhao, S. Yang and H. Yan, *J. Mater. Chem. A*, 2015, **3**, 9098–9102.
- 1000 W. Chen, Y. Wu, Y. Yue, J. Liu, W. Zhang, X. Yang, H. Chen, E. Bi, I. Ashraful, M. Grätzel and L. Han, *Science*, 2015, **350**, 944–948.
- 1001 D. Luo, W. Yang, Z. Wang, A. Sadhanala, Q. Hu, R. Su, R. Shivanna, G. F. Trindade, J. F. Watts, Z. Xu, T. Liu, K. Chen, F. Ye, P. Wu, L. Zhao, J. Wu, Y. Tu, Y. Zhang, X. Yang, W. Zhang, R. H. Friend, Q. Gong, H. J. Snaith and R. Zhu, *Science*, 2018, **360**, 1442–1446.
- 1002 R. Wang, M. Mujahid, Y. Duan, Z. K. Wang, J. Xue and Y. Yang, *Adv. Funct. Mater.*, 2019, **29**, 1808843.
- 1003 T. A. Berhe, W. N. Su, C. H. Chen, C. J. Pan, J. H. Cheng, H. M. Chen, M. C. Tsai, L. Y. Chen, A. A. Dubale and B. J. Hwang, *Energy Environ. Sci.*, 2016, **9**, 323–356.
- 1004 G. Niu, X. Guo and L. Wang, *J. Mater. Chem. A*, 2015, **3**, 8970–8980.
- 1005 Z. Li, M. Yang, J. S. Park, S. H. Wei, J. J. Berry and K. Zhu, *Chem. Mater.*, 2005, **28**, 284–292.
- 1006 G. Schileo and G. Grancini, *J. Phys.: Energy*, 2020, **2**, 021005.
- 1007 N. Rajamanickam, S. Kumari, V. K. Vendra, B. Lavery, J. Spurgeon, T. Druffel and M. K. Sunkara, *Nanotechnology*, 2016, **27**, 235404.
- 1008 N. Aristidou, I. Sanchez-Molina, T. Chotchuangchuchaval, M. Brown, L. Martinez, T. Rath and S. A. Haque, *Angew. Chem., Int. Ed.*, 2015, **54**, 8208.
- 1009 C.-G. Wu, C.-H. Chiang, Z.-L. Tseng, K. N. Mohammad, A. Hagfeldt and M. Gratzel, *Energy Environ. Sci.*, 2015, **8**, 2725–2733.
- 1010 D. Bryant, N. Aristidou, S. Pont, I. Sanchez-Molina, T. Chotchuangchuchaval, S. Wheeler, J. R. Durrant and S. A. Haque, *Energy Environ. Sci.*, 2016, **9**, 1655.
- 1011 B. Conings, J. Drijkoningen, N. Gauquelin, A. Babayigit, J. D'Haen, L. D'Olieslaeger, A. Ethirajan, J. Verbeeck, J. Manca, E. Mosconi and D. De Angelis, *Adv. Energy Mater.*, 2015, **5**, 1500477.
- 1012 X. Li, M. Tschumi, H. Han, S. S. Babkair, R. A. Alzubaydi, A. A. Ansari, S. S. Habib, M. K. Nazeeruddin, S. M. Zakeeruddin and M. Gratzel, *Energy Technol.*, 2015, **3**, 551–555.
- 1013 Y. Zhang, M. Liu, G. E. Eperon, T. C. Leijtens, D. McMeekin, M. Saliba, W. Zhang, M. de Bastiani, A. Petrozza, L. M. Herz and M. B. Johnston, *Mater. Horiz.*, 2015, **2**, 315–322.
- 1014 M. De Bastiani, G. Dell'Erba, M. Gandini, V. D'Innocenzo, S. Neutzner, A. R. S. Kandada, G. Grancini, M. Binda, M. Prato, J. M. Ball, M. Caironi and A. Petrozza, *Adv. Energy Mater.*, 2016, **6**, 1.
- 1015 T. Xu, L. Chen, Z. Guo and T. Ma, *Phys. Chem. Chem. Phys.*, 2016, **18**, 27026.
- 1016 F. Bella, G. Griffini, G. Saracco, M. Grätzel, A. Hagfeldt, S. Turri and C. Gerbaldi, *Science*, 2016, **354**, 203–206.
- 1017 L. Shi, M. P. Bucknall, T. L. Young, M. Zhang, L. Hu, J. Bing, J. Kim, T. Wu, N. Takamure, D. R. McKenzie and S. Huang, *Science*, 2020, **368**, eaba2412.
- 1018 T. Matsui, T. Yamamoto, T. Nishihara, R. Morisawa, T. Yokoyama, T. Sekiguchi and T. Negami, *Adv. Mater.*, 2019, **31**, 1806823.
- 1019 M. Saliba, T. Matsui, J. Y. Seo, K. Domanski, J. P. Correa-Baena, M. K. Nazeeruddin, S. M. Zakeeruddin, W. Tress, A. Abate, A. Hagfeldt and M. Grätzel, *Energy Environ. Sci.*, 2016, **9**, 1989–1997.
- 1020 S. H. Turren-Cruz, A. Hagfeldt and M. Saliba, *Science*, 2018, **362**, 449–453.
- 1021 K. A. Bush, K. Frohna, R. Prasanna, R. E. Beal, T. Leijtens, S. A. Swifter and M. D. McGehee, *ACS Energy Lett.*, 2018, **3**, 428–435.
- 1022 T. H. Han, J. W. Lee, C. Choi, S. Tan, C. Lee, Y. Zhao, Z. Dai, N. De Marco, S. J. Lee, S. H. Bae and Y. Yuan, *Nat. Commun.*, 2019, **10**, 1–10.
- 1023 Y. Zhao, P. Zhu, M. Wang, S. Huang, Z. Zhao, S. Tan, T. H. Han, J. W. Lee, T. Huang, R. Wang and J. Xue, *Adv. Mater.*, 2020, **32**, 1907769.
- 1024 X. Li, M. I. Dar, C. Yi, J. Luo, M. Tschumi, S. M. Zakeeruddin, M. K. Nazeeruddin, H. Han and M. Grätzel, *Nat. Chem.*, 2015, **7**, 703–711.
- 1025 L. Zuo, H. Guo, D. W. deQuilettes, S. Jariwala, N. De Marco, S. Dong, R. DeBlock, D. S. Ginger, B. Dunn, M. Wang and Y. Yang, *Sci. Adv.*, 2017, **3**, e1700106.
- 1026 S. Bai, P. Da, C. Li, Z. Wang, Z. Yuan, F. Fu, M. Kawecki, X. Liu, N. Sakai, J. T. W. Wang and S. Huettner, *Nature*, 2019, **571**, 245–250.
- 1027 Y. Zhang, Z. Fei, P. Gao, Y. Lee, F. F. Tirani, R. Scopelliti, Y. Feng, P. J. Dyson and M. K. Nazeeruddin, *Adv. Mater.*, 2017, **29**, 1702157.
- 1028 D. Yang, X. Zhou, R. Yang, Z. Yang, W. Yu, X. Wang, C. Li, S. F. Liu and S. R. P. Chang, *Energy Environ. Sci.*, 2016, **9**, 3071–3078.
- 1029 S. Dastidar, D. A. Egger, L. Z. Tan, S. B. Cromer, A. D. Dillon, S. Liu, L. Kronik, A. M. Rappe and A. T. Fafarman, *Nano Lett.*, 2016, **16**, 3563–3570.
- 1030 O. A. Syzgantseva, M. Saliba, M. Grätzel and U. Rothlisberger, *J. Phys. Chem. Lett.*, 2017, **8**, 1191–1196.
- 1031 A. Swarnkar, W. J. Mir and A. Nag, *ACS Energy Lett.*, 2018, **3**, 286–289.



- 1032 S. Wu, R. Chen, S. Zhang, B. H. Babu, Y. Yue, H. Zhu, Z. Yang, C. Chen, W. Chen, Y. Huang and S. Fang, *Nat. Commun.*, 2019, **10**, 1–11.
- 1033 S. You, H. Wang, S. Bi, J. Zhou, L. Qin, X. Qiu, Z. Zhao, Y. Xu, Y. Zhang, X. Shi and H. Zhou, *Adv. Mater.*, 2018, **30**, 1706924.
- 1034 J. Chen, S. G. Kim and N. G. Park, *Adv. Mater.*, 2018, **30**, 1801948.
- 1035 Z. Zhu, C. C. Chueh, F. Lin and A. K. Y. Jen, *Adv. Sci.*, 2016, **3**, 1600027.
- 1036 M. Acik and S. B. Darling, *J. Mater. Chem. A*, 2016, **4**, 6185.
- 1037 A. Agresti, S. Pescetelli, B. Taheri, A. E. Del Rio Castillo, L. Cinà, F. Bonaccorso and A. Di Carlo, *ChemSusChem*, 2016, **9**, 2609–2619.
- 1038 C. Petridis, George Kakavelakis and E. Kymakis, *Energy Environ. Sci.*, 2018, **11**, 1030–1061.
- 1039 N. Arora, M. I. Dar, A. Hinderhofer, N. Pellet, F. Schreiber, S. M. Zakeeruddin and M. Grätzel, *Science*, 2017, **358**, 768–771.
- 1040 G. Kakavelakis, I. Paradisanos, B. Paci, A. Generosi, M. L. Papachatzakis, T. Maksudov, L. Najafi, A. E. Del Rio Castillo, G. Kioseoglou, E. Stratakis, F. Bonaccorso and E. Kymakis, *Adv. Energy Mater.*, 2018, **8**, 1702287.
- 1041 A. A. Sultanto, R. Szostak, N. Drigo, V. I. Quelo, P. E. Marchezi, J. C. Germino, H. C. Tolentino, M. K. Nazeeruddin, A. F. Nogueira and G. Grancini, *Nano Lett.*, 2020, **20**, 3992–3998.
- 1042 A. A. Sultanto, N. Drigo, V. I. Quelo, I. Garcia-Benito, A. R. Kirmani, L. J. Richter, P. A. Schouwink, K. T. Cho, S. Paek, M. K. Nazeeruddin and G. Grancini, *J. Mater. Chem. A*, 2020, **8**, 2343–2348.
- 1043 K. T. Cho, Y. Zhang, S. Orlandi, M. Cavazzini, I. Zimmermann, A. Lesch, N. Tabet, G. Pozzi, G. Grancini and M. K. Nazeeruddin, *Nano Lett.*, 2018, **18**, 5467–5474.
- 1044 T. Kuila, S. Bose, A. K. Mishra, P. Khanra, N. H. Kim and J. H. Lee, *Prog. Mater. Sci.*, 2012, **57**, 1061–1105.
- 1045 X. Zhao, S. Liu, H. Zhang, S. Y. Chang, W. Huang, B. Zhu, Y. Shen, C. Shen, D. Wang, Y. Yang and M. Wang, *Adv. Funct. Mater.*, 2019, **29**, 1805168.
- 1046 G. S. Han, Y. H. Song, Y. U. Jin, J. W. Lee, N. G. Park, B. K. Kang, J. K. Lee, I. S. Cho, D. H. Yoon and H. S. Jung, *ACS Appl. Mater. Interfaces*, 2015, **7**, 23521–23526.
- 1047 T. Umeyama, D. Matano, J. Baek, S. Gupta, S. Ito, V. (Ravi) Subramanian and H. Imahori, *Chem. Lett.*, 2015, **44**, 1410–1412.
- 1048 Q. Luo, Y. Zhang, C. Liu, J. Li, N. Wang and H. Lin, *J. Mater. Chem. A*, 2015, **00**, 1–9.
- 1049 R. Ishikawa, S. Watanabe, S. Yamazaki, T. Oya and N. Tsuboi, *ACS Appl. Energy Mater.*, 2019, **2**, 171–175.
- 1050 J.-S. Yeo, R. Kang, S. Lee, Y.-J. Jeon, N. Myoung, C.-L. Lee, D.-Y. Kim, J.-M. Yun, Y.-H. Seo, S.-S. Kim and S.-I. Na, *Nano Energy*, 2014, **12**, 96–104.
- 1051 Z. Wu, S. Bai, J. Xiang, Z. Yuan, Y. Yang, W. Cui, X. Gao, Z. Liu, Y. Jin and B. Sun, *Nanoscale*, 2014, **6**, 10505–10510.
- 1052 A. Agresti, S. Pescetelli, L. Cinà, D. Konios, G. Kakavelakis, E. Kymakis and A. Di Carlo, *Adv. Funct. Mater.*, 2016, **26**, 2686–2694.
- 1053 A. L. Palma, L. Cinà, S. Pescetelli, A. Agresti, M. Raggio, R. Paolesse, F. Bonaccorso and A. Di Carlo, *Nano Energy*, 2016, **22**, 349–360.
- 1054 J. Ye, X.-L. Li, J. Zhao, X. Mei and Q. Li, *RSC Adv.*, 2016, **6**, 36356–36361.
- 1055 L. Q. Zhang, X. W. Zhang, Z. G. Yin, Q. Jiang, X. Liu, J. H. Meng, Y. J. Zhao and H. L. Wang, *J. Mater. Chem. A*, 2015, **3**, 12133–12138.
- 1056 J. Cao, Y. M. Liu, X. Jing, J. Yin, J. Li, B. Xu, Y. Z. Tan and N. Zheng, *J. Am. Chem. Soc.*, 2015, **137**, 10914–10917.
- 1057 F. Wang, M. Endo, S. Mouri, Y. Miyauchi, Y. Ohno, A. Wakamiya, Y. Murata and K. Matsuda, *Nanoscale*, 2016, **8**, 11882–11888.
- 1058 N. Rajamanickam, S. Kumari, V. K. Vendra, B. W. Lavery, J. Spurgeon, T. Druffel and M. K. Sunkara, *Nanotechnology*, 2016, **27**, 235404.
- 1059 D.-Y. Lee, S.-I. Na and S.-S. Kim, *Nanoscale*, 2015, **8**, 1513–1522.
- 1060 J. Kim, A. Ho-Baillie and S. Huang, *Sol. RRL*, 2019, **3**, 1800302.
- 1061 C. Zhang, D. B. Kuang and W. Q. Wu, *Small Methods*, 2020, **4**, 1900662.
- 1062 A. Krishna, S. Gottis, M. K. Nazeeruddin and F. Sauvage, *Adv. Funct. Mater.*, 2019, **29**, 1806482.
- 1063 N. E. Courtier, J. M. Cave, J. M. Foster, A. B. Walker and G. Richardson, *Energy Environ. Sci.*, 2019, **12**, 396–409.
- 1064 I. M. Hermes, Y. Hou, V. W. Bergmann, C. J. Brabec and S. A. Weber, *J. Phys. Chem. Lett.*, 2018, **9**, 6249–6256.
- 1065 E. Edri, S. Kirmayer, A. Henning, S. Mukhopadhyay, K. Gartsman, Y. Rosenwaks, G. Hodes and D. Cahen, *Nano Lett.*, 2014, **14**, 1000–1004.
- 1066 Y. Zhao, A. M. Nardes and K. Zhu, *Faraday Discuss.*, 2015, **176**, 301–312.
- 1067 Y. Bai, I. Mora-Seró, F. De Angelis, J. Bisquert and P. Wang, *Chem. Rev.*, 2014, **114**, 10095–10130.
- 1068 R. Lindblad, D. Bi, B. W. Park, J. Oscarsson, M. Gorgoi, H. Siegbahn, M. Odelius, E. M. Johansson and H. Rensmo, *J. Phys. Chem. Lett.*, 2014, **5**, 648–653.
- 1069 P. Fonteyn, S. Lizin and W. Maes, *Sol. Energy Mater. Sol. Cells*, 2020, **207**, 110325.
- 1070 C. H. Chao, C. H. Chan, J. J. Huang, L. S. Chang and H. C. Shih, *Curr. Appl. Phys.*, 2011, **11**, S136–S139.
- 1071 J. Rensmo, K. Keis, H. Lindstorm, S. Sodergren, A. Solbrand, A. Hagfeldt, E. Lindquist, L. N. Wang and M. Muhammed, *J. Phys. Chem. B*, 1997, **101**, 2598–2601.
- 1072 R. Chakravarty and C. Periasamym, *Sci. Adv. Mater.*, 2011, **3**, 276–283.
- 1073 I. Robel, V. Subramanian, M. Kuno and P. V. Kamat, *J. Am. Chem. Soc.*, 2006, **128**, 2385–2393.
- 1074 M. H. Kumar, N. Yantara, S. Dharani, M. Graetzel, S. Mhaisalkar, P. P. Boix and N. Mathews, *Chem. Commun.*, 2013, **49**, 11089.
- 1075 E. Edri, S. Kirmayer, D. Cahen and G. Hodes, *J. Phys. Chem. Lett.*, 2013, **4**, 897.
- 1076 D. Bi, S.-J. Moon, L. Haggman, G. Boschloo, L. Yang, E. M. J. Johansson, M. K. Nazeeruddin, M. Gratzel and A. Hagfeldt, *RSC Adv.*, 2013, **3**, 18762.



- 1077 H. S. Kim, I. Mora-Sero, V. Gonzalez-Pedro, F. Fabregat-Santiago, E. J. Juarez-Perez, N. G. Park and J. Bisquert, *Nat. Commun.*, 2013, **4**, 2242.
- 1078 S. H. Hwang, J. Roh, J. Lee, J. Ryu, J. Yun and J. Jang, *J. Mater. Chem. A*, 2014, **2**, 16429.
- 1079 Y. H. Hu, *Adv. Mater.*, 2014, **26**, 2102.
- 1080 A. Bera, K. Wu, A. Sheikh, E. Alarousu, O. F. Mohammed and T. Wu, *J. Phys. Chem. C*, 2014, **118**, 28494–28501.
- 1081 C. Wang, Y. Tang, Y. Hu, L. Huang, J. Fu, J. Jin, W. Shi, L. Wang and W. Yang, *RSC Adv.*, 2015, **5**, 52041–52047.
- 1082 S. S. Mali, C. S. Shim and C. K. Hong, *Sci. Rep.*, 2015, **5**, 11424.
- 1083 C. Sun, L. Guan, Y. Guo, B. Fang, J. Yang, H. Duan, Y. Chen, H. Li and H. Liu, *J. Alloys Compd.*, 2017, **722**, 196–206.
- 1084 O. N. Tufte and P. W. Chapman, *Phys. Rev.*, 1967, **155**, 796.
- 1085 Q. Zhang, C. S. Dandeneau, X. Zhou and G. Cao, *Adv. Mater.*, 2009, **21**, 4087.
- 1086 H. Zhou, Q. Chen, G. Li, S. Luo, T. B. Song, H. S. Duan, Z. Hong, J. You, Y. Liu and Y. Yang, *Science*, 2014, **345**, 542–546.
- 1087 M. M. Tavakoli, Q. Lin, S. F. Leung, G. C. Lui, H. Lu, L. Li, B. Xiang and Z. Fan, *Nanoscale*, 2016, **8**, 4276–4283.
- 1088 J. M. Marin-Beloqui, L. Lanzetta and E. Palomares, *Chem. Mater.*, 2016, **28**, 207–213.
- 1089 E. M. Hutter, G. E. Eperon, S. D. Stranks and T. J. Savenije, *J. Phys. Chem. Lett.*, 2015, **6**, 3082–3090.
- 1090 Y. Wang, H.-Y. Wang, M. Yu, L. Fu, Y. Qin, J.-P. Zhang and X. Ai, *Phys. Chem. Chem. Phys.*, 2015, **17**, 29501–29506.
- 1091 K. Sveinbjörnsson, K. Aitola, X. Zhang, M. Pazoki, A. Hagfeldt, G. Boschloo and E. M. J. Johansson, *J. Phys. Chem. Lett.*, 2015, **6**, 4259–4264.
- 1092 A. Listorti, E. J. Juarez-Perez, C. Frontera, V. Rofati, L. Garcia-Andrade, S. Colella, A. Rizzo, P. Ortiz and I. Mora-Sero, *J. Phys. Chem. Lett.*, 2015, **6**, 1628–1637.
- 1093 Y. Zhao, A. M. Nardes and K. Zhu, *J. Phys. Chem. Lett.*, 2014, **5**, 490–494.
- 1094 D. H. Kim, G. S. Han, W. M. Seong, J.-W. Lee, B. J. Kim, N.-G. Park, K. S. Hong, S. Lee and H. S. Jung, *ChemSusChem*, 2015, **8**, 2392–2398.
- 1095 B. Roose, K. C. Gödel, S. Pathak, A. Sadhanala, J. P. C. Baena, B. D. Wilts, H. J. Snaith, U. Wiesner, M. Grätzel, U. Steiner and A. Abate, *Adv. Energy Mater.*, 2016, **6**, 1501868–1501874.
- 1096 H.-S. Kim, J.-W. Lee, N. Yantara, P. P. Boix, S. A. Kulkarni, S. Mhaisalkar, M. Grätzel and N.-G. Park, *Nano Lett.*, 2013, **13**, 2412–2417.
- 1097 R. Salazar, M. Altomare, K. Lee, J. Tripathy, R. Kirchgeorg, N. T. Nguyen, M. Mokhtar, A. Alshehri, S. A. Al-Thabaiti and P. Schmuki, *ChemElectroChem*, 2015, **2**, 824.
- 1098 S. Dharani, H. K. Mulmudi, N. Yantara, P. T. Thu Trang, N. G. Park, M. Graetzel, S. Mhaisalkar, N. Mathews and P. P. Boix, *Nanoscale*, 2014, **6**, 1675–1679.
- 1099 B. Li, Y. Chen, Z. Liang, D. Gao and W. Huang, *RSC Adv.*, 2015, **5**, 94290–94295.
- 1100 M. M. Tavakoli, R. Tavakoli, Z. Nourbakhsh, A. Waleed, U. S. Virk and Z. Fan, *Adv. Mater. Interfaces*, 2016, **3**, 1500790.
- 1101 J. T. W. Wang, J. M. Ball, E. M. Barea, A. Abate, J. A. Alexander-Webber, J. Huang, M. Saliba, I. Mora-Sero, J. Bisquert, H. J. Snaith and R. J. Nicholas, *Nano Lett.*, 2013, **14**, 724–729.
- 1102 Z. Zhu, J. Ma, Z. Wang, C. Mu, Z. Fan, L. Du, Y. Bai, L. Fan, H. Yan, D. L. Phillips and S. Yang, *J. Am. Chem. Soc.*, 2014, **25**, 3760–3763.
- 1103 M. M. Tavakoli, R. Tavakoli, S. Hasanzadeh and M. H. Mirfasihi, *J. Phys. Chem. C*, 2016, **120**, 19531–19536.
- 1104 S. Ameen, M. S. Akhtar, H.-K. Seo, M. K. Nazeeruddin and H.-S. Shin, *J. Phys. Chem. C*, 2015, **119**, 10379–10390.
- 1105 F. Biccari, F. Gabelloni, E. Burzi, M. Gurioli, S. Pescetelli, A. Agresti, A. E. Del Rio Castillo, A. Ansaldo, E. Kymakis, F. Bonaccorso, A. Di Carlo and A. Vinattieri, *Adv. Energy Mater.*, 2017, **22**, 1701349–1701356.
- 1106 Y. Busby, A. Agresti, S. Pescetelli, A. Di Carlo, C. Noel, J. J. Pireaux and L. Houssiau, *Mater. Today Energy*, 2018, **9**, 1–10.
- 1107 P. O’Keeffe, D. Catone, A. Paladini, F. Toschi, S. Turchini, L. Avaldi, F. Martelli, A. Agresti, S. Pescetelli, A. E. Del Rio Castillo and F. Bonaccorso, *Nano Lett.*, 2019, **19**, 684–691.
- 1108 A. Agresti, S. Pescetelli, A. L. Palma, A. E. Del Rio Castillo, D. Konios, G. Kakavelakis, S. Razza, L. Cinà, E. Kymakis, F. Bonaccorso and A. Di Carlo, *ACS Energy Lett.*, 2017, **2**, 279–287.
- 1109 K. Cho, G. Grancini, Y. Lee, D. Konios, S. Paek, E. Kymakis and M. K. Nazeeruddin, *ChemSusChem*, 2016, **9**, 3040–3044.
- 1110 J. Ryu, J. W. Lee, H. Yu, J. Yun, K. Lee, J. Lee, D. Hwang, J. Kang, S. K. Kim and J. Jang, *J. Mater. Chem. A*, 2017, **5**, 16834–16842.
- 1111 S. S. Mali, C. S. Shim, H. Kima and C. K. Hong, *J. Mater. Chem. A*, 2016, **4**, 12158–12169.
- 1112 M. Zhu, W. Liu, W. Ke, L. Xie, P. Dong and F. Hao, *ACS Appl. Mater. Interfaces*, 2018, **11**, 666–673.
- 1113 X. Zhao, L. Tao, H. Li, W. Huang, P. Sun, J. Liu, S. Liu, Q. Sun, Z. Cui, L. Sun, Y. Shen, Y. Yang and M. Wang, *Nano Lett.*, 2018, **18**, 2442.
- 1114 Z. Liu, S. Wu, X. Yang, Y. Zhou, J. Jin, J. Sunc, L. Zhao and S. Wang, *Nanoscale Adv.*, 2020, **2**, 5396–5402.
- 1115 P. Huang, L. Yuan, K. Zhang, Q. Chen, Y. Zhou, B. Song and Y. Li, *ACS Appl. Mater. Interfaces*, 2018, **10**, 14796.
- 1116 P. Huang, Q. Chen, K. Zhang, L. Yuan, Y. Zhou, B. Song and Y. Li, *J. Mater. Chem. A*, 2019, **7**, 6213.
- 1117 N. Fu, C. Huang, P. Lin, M. Zhu, T. Li, M. Ye, S. Lin, G. Zhang, J. Du, C. Liu and B. Xu, *J. Mater. Chem. A*, 2018, **6**, 8886–8894.
- 1118 P. Patil, D. S. Mann, U. T. Nakate, Y. B. Hahn, S. N. Kwon and S. I. Na, *Chem. Eng. J.*, 2020, **397**, 125504.
- 1119 N. Alias, A. Ali Umar, N. A. A. Malek, K. Liu, X. Li, N. A. Abdullah, M. M. Rosli, M. Y. Abd Rahman, Z. Shi, X. Zhang and H. Zhang, *ACS Appl. Mater. Interfaces*, 2021, **13**, 3051–3061.



- 1120 D. Saranin, S. Pescetelli, A. Pazniak, D. Rossi, A. Liedl, A. Yakusheva, L. Luchnikov, D. Podgorny, P. Gostishev, S. Didenko and A. Tameev, *Nano Energy*, 2021, **82**, 105771.
- 1121 J. Chen, J. Zhang, C. Huang, Z. Bi, X. Xu and H. Yu, *Chem. Eng. J.*, 2021, **410**, 128436.
- 1122 M. Batmunkh, K. Vimalanathan, C. Wu, A. S. R. Bati, L. Yu, S. A. Tawfik, M. J. Ford, T. J. Macdonald, C. L. Raston, S. Priya, C. T. Gibson and J. G. Shapter, *Small*, 2019, **3**, 1800521.
- 1123 D. Tsikritzis, K. Rogdakis, K. Chatzimanolis, M. Petrović, N. Tzoganakis, L. Najafi, B. Martín-García, R. Oropesa-Nuñez, S. Bellani, A. Del Rio Castillo and M. Prato, *Mater. Adv.*, 2020, **1**, 450–462.
- 1124 E. Castro, T. J. Sisto, E. L. Romero, F. Liu, S. R. Peurifoy, J. Wang, X. Zhu, C. Nuckolls and L. Echegoyen, *Angew. Chem., Int. Ed.*, 2017, **56**, 14648–14652.
- 1125 L. Yang, Y. Dall'Agnese, K. Hantanasirisakul, C. E. Shuck, K. Maleski, M. Alhabeib, G. Chen, Y. Gao, Y. Sanehira, A. K. Jena, L. Shen, C. Dall'Agnese, X.-F. Wang, Y. Gogotsi and T. Miyasaka, *J. Mater. Chem. A*, 2019, **7**, 5635.
- 1126 A. Agresti, A. Pazniak, S. Pescetelli, A. Di Vito, D. Rossi, A. Pecchia, M. Auf der Maur, A. Liedl, R. Larciprete, D. V. Kuznetsov, D. Saranin and A. Di Carlo, *Nat. Mater.*, 2019, **18**, 1228–1234.
- 1127 K. Chatzimanolis, K. Rogdakis, D. Tsikritzis, N. Tzoganakis, M. Tountas, M. Krassas, S. Bellani, L. Najafi, B. Martín-García, R. Oropesa-Nuñez and M. Prato, *Nanoscale Adv.*, 2021, **3**, 3124–3135.
- 1128 Z. Xiao, Q. Dong, C. Bi, Y. Shao, Y. Yuan and J. Huang, *Adv. Mater.*, 2014, **26**, 6503.
- 1129 W. Nie, H. Tsai, R. Asadpour, J.-C. Blancon, A. J. Neukirch, G. Gupta, J. J. Crochet, M. Chhowalla, S. Tretiak, M. A. Alam, H.-L. Wang and A. D. Mohite, *Science*, 2015, **347**, 522.
- 1130 Z. Liang, S. Zhang, X. Xu, N. Wang, J. Wang, X. Wang, Z. Bi, G. Xu, N. Yuan and J. Ding, *RSC Adv.*, 2015, **5**, 60562.
- 1131 C. Roldan-Carmona, O. Malinkiewicz, R. Betancur, G. Longo, C. Momblona, F. Jaramillo, L. Camacho and H. J. Bolink, *Energy Environ. Sci.*, 2014, **7**, 2968.
- 1132 D. Bi, W. Tress, M. I. Dar, P. Gao, J. Luo, C. Renevier, K. Schenk, A. Abate, F. Giordano, J.-P. Correa Baena, J.-D. Decoppet, S. M. Zakeeruddin, M. K. Nazeeruddin, M. Grätzel and A. Hagfeldt, *Sci. Adv.*, 2016, **2**, e150117.
- 1133 H.-S. Kim and N.-G. Park, *J. Phys. Chem. Lett.*, 2014, **5**, 2927.
- 1134 P. You, G. Tang and F. Yan, *Mater. Today Energy*, 2019, **11**(11), 128–158.
- 1135 M. Hadadian, J.-P. Correa-Baena, E. K. Goharshadi, A. Ummadisisingu, J.-Y. Seo, J. Luo, S. Gholipour, S. M. Zakeeruddin, M. Saliba, A. Abate, M. Grätzel and A. Hagfeldt, *Adv. Mater.*, 2016, **28**, 8681–8686.
- 1136 C.-C. Chung, S. Narra, E. Jokar, H.-P. Wu and E. W.-G. Diau, *J. Mater. Chem. A*, 2017, **5**, 13957.
- 1137 X. Fang, J. Ding, N. Yuan, P. Sun, M. Lv, G. Ding and C. Zhu, *Phys. Chem. Chem. Phys.*, 2017, **19**, 6057–6063.
- 1138 W. Wang, H. Zhang, T. Zhang, W. Shi, M. Kan, J. Chen and Y. Zhao, *Sol. RRL*, 2019, **3**, 1900197.
- 1139 W. Yang, J. Chen, X. Lian, J. Li, F. Yao, G. Wu, W. Qiu, C. Jin, P. Heremans and H. Chen, *Sol. RRL*, 2019, **3**, 1900132.
- 1140 X. Gong, L. Guan, Q. Li, Y. Li, T. Zhang, H. Pan, Q. Sun, Y. Shen, C. Grätzel, S. M. Zakeeruddin and M. Grätzel, *Sci. Adv.*, 2020, **6**, eaay5661.
- 1141 D. Li, A. E. Del Rio Castillo, H. Jussila, G. Ye, Z. Ren, J. Bai, X. Chen, H. Lipsanen, Z. Sun and F. Bonaccorso, *Appl. Mater. Today*, 2016, **4**, 17–23.
- 1142 T. Mahmoudi, Y. Wang and Y.-B. Hahn, *ACS Energy Lett.*, 2019, **4**, 235–241.
- 1143 Z. Guo, L. Gao, Z. Xu, S. Teo, C. Zhang, Y. Kamata, S. Hayase and T. Ma, *Small*, 2018, **14**, 1802738.
- 1144 R. Y. Hu, Y. Zhang, S. Paek, X.-X. Gao, X. Li and M. K. Nazeeruddin, *J. Mater. Chem. A*, 2020, **8**, 8058–8064.
- 1145 J. A. Christians, R. C. M. Fung and P. V. Kamat, *J. Am. Chem. Soc.*, 2014, **136**, 758–764.
- 1146 T. Leijtens, G. E. Eperon, S. Pathak, A. Abate, M. M. Lee and H. J. Snaith, *Nat. Commun.*, 2013, **4**, 2885.
- 1147 J. You, Z. Hong, Y. Yang, Q. Chen, M. Cai, T.-B. Song, C.-C. Chen, S. Lu, Y. Liu, H. Zhou and Y. Yang, *ACS Nano*, 2014, **8**, 1674–1680.
- 1148 Y. Chen, Z. Yang, S. Wang, X. Zheng, Y. Wu, N. Yuan, W. H. Zhang and S. Liu, *Adv. Mater.*, 2018, **30**, 1805660.
- 1149 H. Wang, X. Zeng, Z. Huang, W. Zhang, X. Qiao, B. Hu, X. Zou, M. Wang, Y. B. Cheng and W. Chen, *ACS Appl. Mater. Interfaces*, 2014, **6**, 12609–12617.
- 1150 J. Sun, J. Lu, B. Li, L. Jiang, A. S. Chesman, A. D. Scully, T. R. Gengenbach, Y. B. Cheng and J. J. Jasieniak, *Nano Energy*, 2018, **49**, 163–171.
- 1151 Y. G. Kim, K. C. Kwon, Q. V. Le, K. Hong, H. W. Jang and S. Y. Kim, *J. Power Sources*, 2016, **319**, 1–8.
- 1152 W. J. Dong, G. H. Jung, S. Y. Kim and J.-L. Lee, *Sol. Energy Mater. Sol. Cells*, 2013, **109**, 240–245.
- 1153 P. Schulz, E. Edri, S. Kirmayer, G. Hodes, D. Cahen and A. Kahn, *Energy Environ. Sci.*, 2014, **7**, 1377.
- 1154 P. W. Liang, C. Y. Liao, C. C. Chueh, F. Zuo, S. T. Williams, X. K. Xin, J. Lin and A. K. Jen, *Adv. Mater.*, 2014, **26**, 3748.
- 1155 S. Wang, X. Huang, H. Sun and C. Wu, *Nanoscale Res. Lett.*, 2017, **12**, 619.
- 1156 X. Huang, H. Guo, J. Yang, K. Wang, X. Niu and X. Liu, *Org. Electron.*, 2016, **39**, 288–295.
- 1157 A. Giuri, S. Masi, S. Colella, A. Kovtun, S. Dell'Elce, E. Treossi, A. Liscio, C. Esposito Corcione, A. Rizzo and A. Listorti, *Adv. Funct. Mater.*, 2016, **26**, 6985–6994.
- 1158 O. Akhavan, E. Ghaderi, S. Aghayee, Y. Fereydooni and A. Talebi, *J. Mater. Chem.*, 2012, **22**, 13773.
- 1159 T. Liu, D. Kim, H. Han, A. R. bin Mohd Yusoff and J. Jang, *Nanoscale*, 2015, **7**, 10708.
- 1160 D. Li, J. Cui, H. Li, D. Huang, M. Wang and Y. Shen, *Sol. Energy*, 2016, **131**, 176–182.
- 1161 G. Tang, P. You, Q. Tai, A. Yang, J. Cao, F. Zheng, Z. Zhou, J. Zhao, P. K. L. Chan and F. Yan, *Adv. Mater.*, 2019, **31**, 1807689.
- 1162 F. Zhang, J. He, Y. Xiang, K. Zheng, B. Xue, S. Ye, X. Peng, Y. Hao, J. Lian, P. Zeng, J. Qu and J. Song, *Adv. Mater.*, 2018, **30**, 1803244.



- 1163 J. Cao, G. Tang, P. You, T. Wang, F. Zheng, J. Zhao and F. Yan, *Adv. Funct. Mater.*, 2020, **30**, 2002358.
- 1164 Y. Wang, S. Wang, X. Chen, Z. Li, J. Wang, T. Li and X. Deng, *J. Mater. Chem. A*, 2018, **6**, 4860.
- 1165 J. H. Kim, P.-W. Liang, S. T. Williams, N. Cho, C.-C. Chueh, M. S. Glaz, D. S. Ginger and A. K.-Y. Jen, *Adv. Mater.*, 2014, **27**, 695–701.
- 1166 Q. V. Le, T. P. Nguyen, K. S. Choi, Y.-H. Cho, Y. J. Hong and S. Y. Kim, *Phys. Chem. Chem. Phys.*, 2014, **16**, 25468–25472.
- 1167 U. Dasgupta, S. Chatterjee and A. J. Pal, *Sol. Energy Mater. Sol. Cells*, 2017, **172**, 353–360.
- 1168 X. Mu, X. Wu, T. Zhang, D. B. Go and T. Luo, *Sci. Rep.*, 2014, **4**, 3909.
- 1169 Z. Ni, M. Ye, J. Ma, Y. Wang, R. Quhe, J. Zheng, L. Dai, D. Yu, J. Shi, J. Yang and S. Watanabe, *Adv. Electron. Mater.*, 2016, **2**, 1600191.
- 1170 J. Chang, L. F. Register and S. K. Banerjee, *Appl. Phys. Lett.*, 2013, **103**, 223509.
- 1171 L. Sygellou, G. Paterakis, C. Galiotis and D. Tasis, *J. Phys. Chem. C*, 2016, **120**, 281–290.
- 1172 R. Garg, N. K. Dutta and N. R. Choudhury, *Nanomaterials*, 2014, **4**, 267–300.
- 1173 H. Wang, H. Yuan, S. S. Hong, Y. Li and Y. Cui, *Chem. Soc. Rev.*, 2015, **44**, 2664–2680.
- 1174 S. Bertolazzi, M. Gobbi, Y. Zhao, C. Backes and P. Samorì, *Chem. Soc. Rev.*, 2018, **47**, 6845–6888.
- 1175 P. Huang, Z. Wang, Y. Liu, K. Zhang, L. Yuan, Y. Zhou, B. Song and Y. Li, *ACS Appl. Mater. Interfaces*, 2017, **9**, 25323–25331.
- 1176 J. Kim, M. A. M. Teridi, A. R. bin Mohd Yusoff and J. Jang, *Sci. Rep.*, 2016, **6**, 27773.
- 1177 Q.-D. Yang, J. Li, Y. Cheng, H.-W. Li, Z. Guan, B. Yub and S.-W. Tsang, *J. Mater. Chem. A*, 2017, **5**, 9852.
- 1178 H. Luo, X. i. Lin, X. Hou, L. Pan, S. i. Huang and X. Chen, *Nano-Micro Lett.*, 2017, **9**, 39.
- 1179 S. Feng, Y. Yang, M. Li, J. Wang, Z. Cheng, J. Li, G. Ji, G. Yin, F. Song, Z. Wang, J. Li and X. Gao, *ACS Appl. Mater. Interfaces*, 2016, **8**, 14503–14512.
- 1180 H. Chen, Y. Hou, C. E. Halbig, S. Chen, H. Zhang, N. Li, F. Guo, X. Tang, N. Gasparini, I. Levchuk and S. Kahmann, *J. Mater. Chem. A*, 2016, **4**, 11604–11610.
- 1181 M. Petrus, T. Bein, T. Dingemans and P. Docampo, *J. Mater. Chem. A*, 2015, **3**, 12159.
- 1182 J. Burschka, A. Dualeh, F. Kessler, E. Baranoff, N.-L. Cevey-Ha, C. Yi, M. K. Nazeeruddin and M. Graetzel, *J. Am. Chem. Soc.*, 2011, **133**, 18042–18045.
- 1183 T. Leijtens, J. Lim, J. Teuscher, T. Park and H. J. Snaith, *Adv. Mater.*, 2013, **25**, 3227.
- 1184 U. Bach, D. Lupo, P. Comte, J. Moser, F. Weissörtel, J. Salbeck, H. Spreitzer and M. Gratzel, *Nature*, 1998, **395**, 583.
- 1185 S. N. Habisreutinger, N. K. Noel, H. J. Snaith and R. J. Nicholas, *Adv. Energy Mater.*, 2017, **7**, 1601079.
- 1186 J. Liu, Y. Wu, C. Qin, X. Yang, T. Yasuda, A. Islam, K. Zhang, W. Peng, W. Chen and L. Han, *Energy Environ. Sci.*, 2014, **7**, 2963–2967.
- 1187 W. Li, H. Dong, L. Wang, N. Li, X. Guo, J. Li and Y. Qiu, *J. Mater. Chem. A*, 2014, **2**, 13587–13592.
- 1188 Q. Luo, Y. Zhang, C. Liu, J. Li, N. Wang and H. Lin, *J. Mater. Chem. A*, 2015, **3**, 15996.
- 1189 M. Zhang, M. Ye, W. Wang, C. Ma, S. Wang, Q. Liu, T. Lian, J. Huang and Z. Lin, *Adv. Mater.*, 2020, **32**, 2000999.
- 1190 A. Capasso, F. Matteocci, L. Najafi, M. Prato, J. Buha, L. Cinà, V. Pellegrini, A. Di Carlo and F. Bonaccorso, *Adv. Energy Mater.*, 2016, **6**, 1600920.
- 1191 A. Agresti, S. Pescetelli, L. Najafi, A. E. Del Rio Castillo, R. Oropesa-Nuñez, Y. Busby, F. Bonaccorso and A. Di Carlo, *Nanotechnology (IEEE-NANO)*, 2017 IEEE 17th International Conference on, July 25–28, Pittsburgh, PA, USA, 2017.
- 1192 L. Najafi, B. Taheri, B. Martin-Garcia, S. Bellani, D. Di Girolamo, A. Agresti, R. Oropesa-Nunez, S. Pescetelli, L. Vesce, E. Calabro and M. Prato, *ACS Nano*, 2018, **12**, 10736–10754.
- 1193 A. Agresti, S. Pescetelli, A.-L. Palma, B. Martin-Garcia, L. Najafi, S. Bellani, L. Moreels, M. Prato, F. Bonaccorso and A. Di Carlo, *ACS Energy Lett.*, 2019, **4**, 1862–1871.
- 1194 Y. Shi, O. V. Prezhdo, J. Zhao and W. A. Saidi, *ACS Energy Lett.*, 2020, **5**, 1346–1354.
- 1195 W. Li, H. Dong, X. Guo, N. Li, J. Li, G. Niu and L. Wang, *J. Mater. Chem. A*, 2014, **2**, 20105.
- 1196 X. Wen, J. Wu, D. Gao and C. Lin, *J. Mater. Chem. A*, 2016, **4**, 13482–13487.
- 1197 C. Sun, Z. Wu, H.-L. Yip, H. Zhang, X.-F. Jiang, Q. Xue, Z. Hu, Z. Hu, Y. Shen, M. Wang, F. Huang and Y. Cao, *Adv. Energy Mater.*, 2015, **6**, 1501534–1501544.
- 1198 H. Li, L. Tao, F. Huang, Q. Sun, X. Zhao, J. Han, Y. Shen and M. Wang, *ACS Appl. Mater. Interfaces*, 2017, **9**, 38967–38976.
- 1199 E. Nouri, Y.-L. Wang, Q. Chen, J.-J. Xu, G. Paterakis, V. Dracopoulos, Z.-X. Xu, D. Tasis, M. R. Mohammadi and P. Lianos, *Electrochim. Acta*, 2017, **233**, 36–43.
- 1200 P. You, G. Tang, J. Cao, D. Shen, T.-W. Ng, Z. Hawash, N. Wang, C.-K. Liu, W. Lu, Q. Tai, Y. Qi, C.-S. Lee and F. Yan, *Light: Sci. Appl.*, 2021, **10**, 68.
- 1201 T. Gatti, S. Casaluci, M. Prato, M. Salerno, F. Di Stasio, A. Ansaldo, E. Menna, A. Di Carlo and F. Bonaccorso, *Adv. Funct. Mater.*, 2016, **26**, 7443–7453.
- 1202 N. Ahn, K. Kwak, M. S. Jang, H. Yoon, B. Y. Lee, J.-K. Lee, P. V. Pikhitsa, J. Byun and M. Choi, *Nat. Commun.*, 2016, **7**, 13422.
- 1203 J. Niu, D. Yang, X. Ren, Z. Yang, Y. Liu, X. Zhu, W. Zhao and S. F. Liu, *Org. Electron.*, 2017, **48**, 165–171.
- 1204 S. K. Muduli, E. Varrla, S. A. Kulkarni, G. Han, K. Thirumal, O. Lev, S. Mhaisalkar and N. Mathews, *J. Power Sources*, 2017, **371**, 156–161.
- 1205 W. Chen, K. Li, Y. Wang, X. Feng, Z. Liao, Q. Su, X. Lin and Z. He, *J. Phys. Chem. Lett.*, 2017, **8**, 591–598.
- 1206 S. Cogal, L. Calio, G. C. Cogal, M. Salado, S. Kazim, L. Oksuz, S. Ahmad and A. U. Oksuz, *Polym. Bull.*, 2018, **75**, 4531–4545.
- 1207 R. Dai, Y. Wang, J. Wang and X. Deng, *ChemSusChem*, 2017, **10**, 2869–2874.



- 1208 Q. Fu, Z. Xu, X. Tang, T. Liu, X. Dong, X. Zhang, N. Zheng, Z. Xie and Y. Liu, *ACS Energy Lett.*, 2021, **6**, 1521–1532.
- 1209 Q.-Q. Chu, B. Ding, J. Peng, H. Shen, X. Li, Y. Liu, C.-X. Li, C.-J. Li, G.-J. Yang, T. P. White and K. R. Catchpole, *J. Mater. Sci. Technol.*, 2019, **35**, 987–993.
- 1210 E. Bi, H. Chen, F. Xie, Y. Wu, W. Chen, Y. Su, A. Islam, M. Gratzel, X. Yang and L. Han, *Nat. Commun.*, 2017, **8**, 15330.
- 1211 P. You, Z. Liu, Q. Tai, S. Liu and F. Yan, *Adv. Mater.*, 2015, **27**, 3632–3638.
- 1212 H. Chen and S. Yang, *Adv. Mater.*, 2017, **29**, 1603994.
- 1213 M. Wu, M. Sun, H. Zhou, J. Y. Ma and T. Ma, *Adv. Funct. Mater.*, 2020, **30**, 1906451.
- 1214 L. Fagiolarì and F. Bella, *Energy Environ. Sci.*, 2019, **12**, 3437–3472.
- 1215 F. Meng, A. Liu, L. Gao, J. Cao, Y. Yan, N. Wang, M. Fan, G. Wei and T. Ma, *J. Mater. Chem. A*, 2019, **7**, 8690–8699.
- 1216 H. Zhang, K. Song, L. Zhu and Q. Meng, *Carbon*, 2020, **168**, 372–391.
- 1217 H. Wang, H. Liu, W. Li, L. Zhu and H. Chen, *Nano Energy*, 2020, **77**, 105160.
- 1218 D. Bogachuk, S. Zouhair, K. Wojciechowski, B. Yang, V. Babu, L. Wagner, B. Xu, J. Lim, S. Mastroianni, H. Pettersson, A. Hagfeldt and A. Hinsch, *Energy Environ. Sci.*, 2020, **13**, 3880–3916.
- 1219 G. Grancini, C. Roldán-Carmona, I. Zimmermann, E. Mosconi, X. Lee, D. Martineau, S. Narbey, F. Oswald, F. De Angelis, M. Graetzel and M. K. Nazeeruddin, *Nat. Commun.*, 2017, **8**, 15684.
- 1220 K. Domanski, J.-P. Correa-Baena, N. Mine, M. K. Nazeeruddin, A. Abate, M. Saliba, W. Tress, A. Hagfeldt and M. Grätzel, *ACS Nano*, 2016, **10**, 6306–6314.
- 1221 Z. Ku, Y. Rong, M. Xu, T. Liu and H. Han, *Sci. Rep.*, 2013, **3**, 3132.
- 1222 Z. Wei, K. Yan, H. Chen, Y. Yi, T. Zhang, X. Long, J. Li, L. Zhang, J. Wang and S. Yang, *Energy Environ. Sci.*, 2014, **7**, 3326–3333.
- 1223 Z. Wei, H. Chen, K. Yan and S. Yang, *Angew. Chem., Int. Ed.*, 2014, **53**, 13239–13243.
- 1224 Y. Keyou, W. Zhanhua, L. Jinkai, C. Haining, Y. Ya, Z. Xiaoli, L. Xia, W. Zilong, W. Jiannong, X. Jianbin and Y. Shihe, *Small*, 2015, **11**, 2269–2274.
- 1225 F. Zhang, X. Yang, H. Wang, M. Cheng and J. Zhao, *ACS Appl. Mater. Interfaces*, 2014, **6**, 16140–16146.
- 1226 Y. Yang, J. Xiao, H. Wei, L. Zhu, D. Li, Y. Luo, H. Wu and Q. Meng, *RSC Adv.*, 2014, **4**, 52825–52830.
- 1227 T. Chen, G. Tong, E. Xu, H. Li, P. Li, Z. Zhu, J. Tang, Y. Qi and Y. Jiang, *J. Mater. Chem. A*, 2019, **7**, 20597–20603.
- 1228 K. Yan, Z. Wei, J. Li, H. Chen, Y. Yi, X. Zheng, X. Long, Z. Wang, J. Wang, J. Xu and S. Yang, *Small*, 2015, **11**, 2269–2274.
- 1229 Y. Zhu, S. Jia, J. Zheng, Y. Lin, Y. Wua and J. Wang, *J. Mater. Chem. C*, 2018, **6**, 3097.
- 1230 P. Mariani, L. Najafi, G. Bianca, M. I. Zappia, L. Gabatel, A. Agresti, S. Pescetelli, A. Di Carlo, S. Bellani and F. Bonaccorso, *ACS Appl. Mater. Interfaces*, 2021, **13**, 22368.
- 1231 C. Zhang, S. Wang, H. Zhang, Y. Feng, W. Tian, Y. Yan, J. Bian, Y. Wang, S. Jin, S. M. Zakeeruddin and M. Grätzel, *Energy Environ. Sci.*, 2019, **12**, 3585–3594.
- 1232 J.-Y. Ma, M. Sun, Y.-Y. Zhu, H. Zhou, K. Wu, J. Xiao and M. Wu, *ChemElectroChem*, 2020, **7**, 1149–1154.
- 1233 J. Cao, F. Meng, L. Gao, S. Yang, Y. Yan, N. Wang, A. Liu, Y. Lia and T. Ma, *RSC Adv.*, 2019, **9**, 34152–34157.
- 1234 S. Wang, X. Huang, H. Sun and C. Wu, *Nanoscale Res. Lett.*, 2017, **12**, 619.
- 1235 X. Yin, P. Chen, M. Que, Y. Xing, W. Que, C. Niu and J. Shao, *ACS Nano*, 2016, **10**, 3630–3636.
- 1236 Y. Li, L. Meng, Y. M. Yang, G. Xu, Z. Hong, Q. Chen, J. You, G. Li, Y. Yang and Y. Li, *Nat. Commun.*, 2016, **7**, 10214.
- 1237 Y. Wang, S. Bai, L. Cheng, N. Wang, J. Wang, F. Gao and W. Huang, High-Efficiency Flexible Solar Cells Based on Organometal Halide Perovskites, *Adv. Mater.*, 2016, **28**, 4532–4540.
- 1238 M. Kaltenbrunner, G. Adam, E. D. Głowacki, M. Drack, R. Schwödiauer, L. Leonat, D. H. Apaydin, H. Groiss, M. C. Scharber, M. S. White, N. S. Sariciftci and S. Bauer, *Nat. Mater.*, 2015, **14**, 1032.
- 1239 J. A. Christians, P. A. M. Herrera and P. V. Kamat, *J. Am. Chem. Soc.*, 2015, **137**, 1530–1538.
- 1240 H. Sung, N. Ahn, M. S. Jang, J.-K. Lee, H. Yoon, N. G. Park and M. Choi, *Adv. Energy Mater.*, 2016, **6**, 1501873.
- 1241 Z. Yao, D. Qu, Y. Guo and H. Huang, *J. Mater. Sci.*, 2019, **54**, 11564–11573.
- 1242 H. Lu, J. Sun, H. Zhang, S. Lu and W. C. H. Choy, *Nanoscale*, 2016, **8**, 5946–5953.
- 1243 B. Wang, J. Iocozzia, M. Zhang, M. Ye, S. Yan, H. Jin, S. Wang, Z. Zou and Z. Lin, *Chem. Soc. Rev.*, 2019, **48**, 4854–4891.
- 1244 M. M. Davy, T. M. Jadel, C. Qin, B. Luyun and G. Mina, *Sustainable Energy Fuels*, 2021, **5**, 34–51.
- 1245 V. Romano, L. Najafi, A. Sutanto, G. Schileo, V. Quelo, S. Bellani, M. Prato, S. Marras, M. Nazeeruddin, G. D'Angelo and F. Bonaccorso, *ChemPlusChem*, 2021, DOI: 10.1002/cplu.202000777.
- 1246 K. Hong, Q. Van Le, S. Y. Kim and H. W. Jang, *J. Mater. Chem. C*, 2018, **6**, 2189–2209.
- 1247 I. García-Benito, C. Quarti, V. I. Quelo, S. Orlandi, I. Zimmermann, M. Cavazzini, A. Lesch, S. Marras, D. Beljonne, G. Pozzi and M. K. Nazeeruddin, *Chem. Mater.*, 2018, **30**, 8211–8220.
- 1248 Y. Liu, S. Akin, L. Pan, R. Uchida, N. Arora, J. V. Milić, A. Hinderhofer, F. Schreiber, A. R. Uhl, S. M. Zakeeruddin and A. Hagfeldt, *Sci. Adv.*, 2019, **5**, eaaw2543.
- 1249 M. E. Bouduban, V. I. Quelo, V. M. Caselli, K. Y. Cho, A. R. Kirmani, S. Paek, C. Roldan-Carmona, L. J. Richter, J. E. Moser, T. J. Savenije and M. K. Nazeeruddin, *J. Phys. Chem. Lett.*, 2019, **10**, 5713–5720.
- 1250 Y. Bai, S. Xiao, C. Hu, T. Zhang, X. Meng, H. Lin, Y. Yang and S. Yang, *Adv. Energy Mater.*, 2017, **7**, 1701038.
- 1251 J. Chen, J.-Y. Seo and N.-G. Park, *Adv. Energy Mater.*, 2018, **8**, 1702714.



- 1252 K. T. Cho, G. Grancini, Y. Lee, E. Oveisi, J. Ryu, O. Almora, M. Tschumi, P. A. Schouwink, G. Seo, S. Heo, J. Park, J. Jang, S. Paek, G. Garcia-Belmonte and M. K. Nazeeruddin, *Energy Environ. Sci.*, 2018, **11**, 952–959.
- 1253 C. Zuo, A. D. Scully, W. L. Tan, F. Zheng, K. P. Ghiggino, D. Vak, H. Weerasinghe, C. R. McNeill, D. Angmo, A. S. Chesman and M. Gao, *Commun. Mater.*, 2020, **1**, 1–10.
- 1254 A. A. Sultanto, P. Caprioglio, N. Drigo, Y. J. Hofstetter, I. Garcia-Benito, V. I. Quelo, D. Neher, M. K. Nazeeruddin, M. Stollerfoht, Y. Vaynzof and G. Grancini, *Chem*, 2021, **7**, 1903.
- 1255 Y. W. Jang, S. Lee, K. M. Yeom, K. Jeong, K. Choi, M. Choi and J. H. Noh, *Nat. Energy*, 2021, **6**, 63–71.
- 1256 X. Zhang, T. Yang, X. Ren, L. Zhang, K. Zhao and S. Liu, *Adv. Energy Mater.*, 2021, **11**, 2002733.
- 1257 Y. Yang, C. Liu, O. A. Syzgantseva, M. A. Syzgantseva, S. Ma, Y. Ding, M. Cai, X. Liu, S. Dai and M. K. Nazeeruddin, *Adv. Energy Mater.*, 2021, **11**, 2002966.
- 1258 J. H. Heo, D. H. Song and S. H. Im, *Adv. Mater.*, 2014, **26**, 8179.
- 1259 G. E. Eperon, S. D. Stranks, C. Menelaou, M. Johnston, L. M. Herz and H. J. Snaith, *Energy Environ. Sci.*, 2014, **7**, 982.
- 1260 S. De Wolf, J. Holovsky, S.-J. Moon, P. Löper, B. Niesen, M. Ledinsky, F.-J. Haug, J.-H. Yum and C. Ballif, *J. Phys. Chem. Lett.*, 2014, **5**, 1035.
- 1261 J. Werner, B. Niesen and C. Ballif, *Adv. Mater. Interfaces*, 2018, **5**, 1700731.
- 1262 Z. J. Yu, M. Leilaieoun and Z. Holman, *Nat. Energy*, 2016, **1**, 1–4.
- 1263 T. Leijtens, K. A. Bush, R. Prasanna and M. D. McGehee, *Nat. Energy*, 2018, **3**, 828–838.
- 1264 J. P. Correa-Baena, M. Saliba, T. Buonassisi, M. Grätzel, A. Abate, W. Tress and A. Hagfeldt, *Science*, 2017, **358**, 739–744.
- 1265 H. Kanda, A. Uzum, H. Nishino, T. Umeyama, H. Imahori, Y. Ishikawa, Y. Uraoka and S. Ito, *ACS Appl. Mater. Interfaces*, 2016, **8**, 33553–33561.
- 1266 J. Werner, G. Dubuis, A. Walter, P. Löper, S. J. Moon, S. Nicolay, M. Morales-Masis, S. De Wolf, B. Niesen and C. Ballif, *Sol. Energy Mater. Sol. Cells*, 2015, **141**, 407–413.
- 1267 S. Albrecht, M. Saliba, J. P. C. Baena, F. Lang, L. Kegelmann, M. Mews, L. Steier, A. Abate, J. Rappich, L. Korte, R. Schlattmann, M. K. Nazeeruddin, A. Hagfeldt, M. Grätzel and B. Rech, *Energy Environ. Sci.*, 2016, **9**, 81–88.
- 1268 Y. Wu, D. Yan, J. Peng, T. Duong, Y. Wan, S. P. Phang, H. Shen, N. Wu, C. Barugkin, X. Fu, S. Surve, D. Grant, D. Walter, T. P. White, K. R. Catchpole and K. J. Weber, *Energy Environ. Sci.*, 2017, **10**, 2472–2479.
- 1269 H. Kanda, A. Uzum, H. Nishino, T. Umeyama, H. Imahori, Y. Ishikawa, Y. Uraoka and S. Ito, *ACS Appl. Mater. Interfaces*, 2016, **8**, 33553–33561.
- 1270 P. Liu, X. Liu, L. Lyu, H. Xie, H. Zhang, D. Niu, H. Huang, C. Bi, Z. Xiao, J. Huang and Y. Gao, *Appl. Phys. Lett.*, 2015, **106**, 193903.
- 1271 F. Lang, M. A. Gluba, S. Albrecht, J. Rappich, L. Korte, B. Rech and N. H. Nickel, *J. Phys. Chem. Lett.*, 2015, **6**, 2745–2750.
- 1272 S. Bae, H. Kim, Y. Lee, X. Xu, J. S. Park, Y. Zheng, J. Balakrishnan, T. Lei, H. R. Kim, Y. I. Song and Y. J. Kim, *Nat. Nanotechnol.*, 2010, **5**, 574–578.
- 1273 J. Zhou, Z. Ren, S. Li, Z. Liang, C. Sury and H. Shen, *Mater. Lett.*, 2018, **220**, 82–85.
- 1274 E. Lamanna, F. Matteocci, E. Calabrò, L. Serenelli, E. Salza, L. Martini, F. Menchini, M. Izzi, A. Agresti, S. Pescetelli, S. Bellani, A. E. Del Rio Castillo, F. Bonaccorso, M. Tucci and A. Di Carlo, *Joule*, 2020, **4**, 865.
- 1275 A. E. Shalan, *Mater. Adv.*, 2020, **1**, 292–309.
- 1276 B. W. Park and S. I. Seok, *Adv. Mater.*, 2019, **31**, 1805337.
- 1277 Y. Zhou and Y. Zhao, *Energy Environ. Sci.*, 2019, **12**, 1495–1511.
- 1278 Q. Wang, N. Phung, D. Di Girolamo, P. Vivo and A. Abate, *Energy Environ. Sci.*, 2019, **12**, 865–886.
- 1279 A. Di Carlo, A. Agresti, F. Brunetti and S. Pescetelli, *J. Phys. Energy*, 2020, **2**, 031003.
- 1280 Z. Zhang, S. Wang, X. Liu, Y. Chen, C. Su, Z. Tang, Y. Li and G. Xing, *Small Methods*, 2021, **5**, 2000937.
- 1281 X. Cai, Y. Luo, B. Liu and H. M. Cheng, *Chem. Soc. Rev.*, 2018, **47**, 6224–6266.
- 1282 G. Hu, L. Yang, Z. Yang, Y. Wang, X. Jin, J. Dai, Q. Wu, S. Liu, X. Zhu, X. Wang and T. C. Wu, *Sci. Adv.*, 2020, **6**, eaba5029.
- 1283 G. Kakavelakis, E. Kymakis and K. Petridis, *Adv. Mater. Interfaces*, 2018, **5**, 1800339.
- 1284 D. Koo, U. Kim, Y. Cho, J. Lee, J. Seo, Y. Choi, K. J. Choi, J. M. Baik, C. Yang and H. Park, *Chem. Mater.*, 2021, **33**, 5563.
- 1285 S. Chen and G. Shi, *Adv. Mater.*, 2017, **29**, 1605448.
- 1286 S. Svanstrom, T. J. Jacobsson, G. Boschloo, E. M. Johansson, H. Rensmo and U. B. Cappel, *ACS Appl. Mater. Interfaces*, 2020, **12**, 7212–7221.
- 1287 S. Zhang and G. Han, *Prog. Energy*, 2020, **2**, 022002.
- 1288 Z. Lin, Y. Liu, U. Halim, M. Ding, Y. Liu, Y. Wang, C. Jia, P. Chen, X. Duan, C. Wang and F. Song, *Nature*, 2018, **562**, 254–258.
- 1289 D. T. Gangadharan and D. Ma, *Energy Environ. Sci.*, 2019, **12**, 2860–2889.
- 1290 J. Peng, J. I. Khan, W. Liu, E. Ugur, T. Duong, Y. Wu, H. Shen, K. Wang, H. Dang, E. Aydin and X. Yang, *Adv. Energy Mater.*, 2018, **8**, 1801208.
- 1291 <https://graphene-flagship.eu/project/spearhead/Pages/Solar-Farm.aspx> (accessed on June 2021).
- 1292 <https://graphene-flagship.eu/innovation/spearheads/c3-sh05-grapes/> (data accessed on June 2021).
- 1293 <https://www.enelgreenpower.com/media/news/2020/11/graphene-project-grapes> (data accessed on June 2021).
- 1294 S. Ma, Y. Bai, H. Wang, H. Zai, J. Wu, L. Li, S. Xiang, N. Liu, L. Liu, C. Zhu and G. Liu, *Adv. Energy Mater.*, 2020, **10**, 1902472.
- 1295 A. Uddin, M. B. Upama, H. Yi and L. Duan, *Coatings*, 2019, **9**, 65.



- 1296 H. K. Seo, M. H. Park, Y. H. Kim, S. J. Kwon, S. H. Jeong and T. W. Lee, *ACS Appl. Mater. Interfaces*, 2016, **8**, 14725–14731.
- 1297 Z. Pan, H. Rao, I. Mora-Seró, J. Bisquert and X. Zhong, *Chem. Soc. Rev.*, 2018, **47**, 7659–7702.
- 1298 J. S. Shaikh, N. S. Shaikh, S. S. Mali, J. V. Patil, S. A. Beknalkar, A. P. Patil, N. L. Tarwal, P. Kanjanaboos, C. K. Hong and P. S. Patil, *ChemSusChem*, 2019, **12**, 4724–4753.
- 1299 S. Emin, S. P. Singh, L. Han, N. Satoh and A. Islam, *Sol. Energy*, 2011, **85**, 1264–1282.
- 1300 T. Sogabe, Q. Shen and K. Yamaguchi, *J. Photonics Energy*, 2016, **6**, 040901.
- 1301 H. K. Jun, M. A. Careem and A. K. Arof, *Renewable Sustainable Energy Rev.*, 2013, **22**, 148–167.
- 1302 V. T. Chebrolu and H. J. Kim, *J. Mater. Chem. C*, 2019, **7**, 4911–4933.
- 1303 Z. Du, M. Artemyev, J. Wang and J. Tang, *J. Mater. Chem. A*, 2019, **7**, 2464–2489.
- 1304 H. Anwar, I. Arif, U. Javeed, H. Mushtaq, K. Ali and S. K. Sharma, *Quantum Dot Solar Cells. In Solar Cells*, Springer, Cham, 2020, pp. 235–258.
- 1305 G. H. Carey, A. L. Abdelhady, Z. Ning, S. M. Thon, O. M. Bakr and E. H. Sargent, *Chem. Rev.*, 2015, **115**, 12732–12763.
- 1306 H. Lee, H. J. Song, M. Shim and C. Lee, *Energy Environ. Sci.*, 2020, **13**, 404–431.
- 1307 O. López-Rojas and J. G. Guzmán, A review on quantum dot solar cells: properties, materials, synthesis and devices, In 2019 IEEE International Conference on Engineering Veracruz (ICEV), 2019, vol. 1, pp. 1–5.
- 1308 J. Tang, X. Wang, L. Brzozowski, D. A. R. Barkhouse, R. Debnath, L. Levina and E. H. Sargent, *Adv. Mater.*, 2010, **22**, 1398–1402.
- 1309 K. W. Johnston, A. G. Pattantyus-Abraham, J. P. Clifford, S. H. Myrskog, S. Hoogland, H. Shukla, E. J. D. Klem and E. H. Sargent, *Appl. Phys. Lett.*, 2008, **92**, 122111.
- 1310 K. W. Johnston, A. G. Pattantyus-Abraham, J. P. Clifford, S. H. Myrskog, D. D. MacNeil, L. Levina and E. H. Sargent, *Appl. Phys. Lett.*, 2008, **92**, 151115.
- 1311 J. P. Clifford, K. W. Johnston, L. Levina and E. H. Sargent, *Appl. Phys. Lett.*, 2007, **91**, 253117.
- 1312 V. T. Mai, N. H. Duong and X. D. Mai, *Mater. Lett.*, 2019, **249**, 37.
- 1313 L. Hu, X. Geng, S. Singh, J. Shi, Y. Hu, S. Li, X. Guan, T. He, X. Li, Z. Cheng and R. Patterson, *Nano Energy*, 2019, **64**, 103922.
- 1314 A. G. Pattantyus-Abraham, I. J. Kramer, A. R. Barkhouse, X. Wang, G. Konstantatos, R. Debnath, L. Levina, I. Raabe, M. K. Nazeeruddin, M. Gratzel and E. H. Sargent, *ACS Nano*, 2010, **4**, 3374–3380.
- 1315 I. J. Kramer, R. Debnath, A. G. Pattantyus-Abraham, A. R. Barkhouse, X. Wang, L. Levina, J. Tang, A. Fischer, G. Konstantatos, M. T. Greiner and Z. H. Lu, Depleted-Heterojunction Colloidal Quantum Dot Solar Cells Employing Low-Cost Metal Contacts. In *Frontiers in Optics* (p. FMA2), *Opt. Soc. Am.*, 2010, DOI: 10.1364/FIO.2010.FMA2.
- 1316 X. Yao, Y. Chang, G. Li, L. Mi, S. Liu, H. Wang, Y. Yu and Y. Jiang, *Sol. Energy Mater. Sol. Cells*, 2015, **137**, 287–292.
- 1317 Y. L. Lee, B. M. Huang and H. T. Chien, *Chem. Mater.*, 2008, **20**, 6903–6905.
- 1318 S. J. Shen and Y. L. Lee, *Nanotechnology*, 2008, **19**, 045602.
- 1319 M. Samadpour, P. P. Boix, S. Giménez, A. Irají Zad, N. Taghavinia, I. Mora-Seró and J. Bisquert, *J. Phys. Chem. C*, 2011, **115**, 14400–14407.
- 1320 S. Q. Fan, D. Kim, J. J. Kim, D. W. Jung, S. O. Kang and J. Ko, *Electrochem. Commun.*, 2009, **11**, 1337–1339.
- 1321 S. Maiti, F. Azlan, Y. Jadhav, J. Dana, P. Anand, S. K. Haram, G. R. Dey and H. N. Ghosh, *Sol. Energy*, 2019, **181**, 195–202.
- 1322 Y. Lu, J. Jia, C. Lu, J. Huang and X. Feng, *Mater. Lett.*, 2019, **243**, 176–179.
- 1323 D. Zhao and C. F. Yang, *Renewable Sustainable Energy Rev.*, 2016, **54**, 1048–1059.
- 1324 T. Archana, K. Vijayakumar, M. Arivanandhan and R. Jayavel, *Surf. Interfaces*, 2019, **17**, 100350.
- 1325 L. Zheng, F. Teng, X. Ye, H. Zheng and X. Fang, *Adv. Energy Mater.*, 2020, **10**, 1902355.
- 1326 J. Tang, H. Liu, D. Zhitomirsky, S. Hoogland, X. Wang, M. Furukawa, L. Levina and E. H. Sargent, *Nano Lett.*, 2012, **12**, 4889–4894.
- 1327 A. K. Rath, M. Bernechea, L. Martinez, F. P. G. de Arquer, J. Osmond and G. Konstantatos, *Nat. Photonics*, 2012, **6**, 529–534.
- 1328 M. Kouhnavard, S. Ikeda, N. A. Ludin, N. A. Khairudin, B. V. Ghaffari, M. A. Mat-Teridi, M. A. Ibrahim, S. Sepeai and K. Sopian, *Renewable Sustainable Energy Rev.*, 2014, **37**, 397–407.
- 1329 C.-H. M. Chuang, P. R. Brown, V. Bulovic and M. G. Bawendi, *Nat. Mater.*, 2014, **13**, 796–801.
- 1330 M. Yuan, D. Zhitomirsky, V. Adinolfi, O. Voznyy, K. W. Kemp, Z. Ning, X. Lan, J. Xu, J. Y. Kim, H. Dong and E. H. Sargent, *Adv. Mater.*, 2013, **25**, 5586–5592.
- 1331 D.-K. Ko, P. R. Brown, M. G. Bawendi and V. Bulovic, *Adv. Mater.*, 2014, **26**, 4845–4850.
- 1332 P. K. Santra and P. V. Kamat, *J. Am. Chem. Soc.*, 2013, **135**, 877–885.
- 1333 X. Wang, G. I. Koleilat, J. Tang, H. Liu, I. J. Kramer, R. Debnath, L. Brzozowski, D. A. R. Barkhouse, L. Levina, S. Hoogland and E. H. Sargent, *Nat. Photon.*, 2011, **5**, 480–484.
- 1334 T. Blachowicz and A. Ehrmann, *Appl. Sci.*, 2020, **10**, 1743.
- 1335 M. Hao, Y. Bai, S. Zeiske, L. Ren, J. Liu, Y. Yuan, N. Zarrabi, N. Cheng, M. Ghasemi, P. Chen, M. Lyu, D. He, J.-H. Yun, Y. Du, Y. Wang, S. Ding, A. Armin, P. Meredith, G. Liu, H.-M. Cheng and L. Wang, *Nat. Energy*, 2020, **5**, 79–88.
- 1336 E. M. Sanehira, A. R. Marshall, J. A. Christians, S. P. Harvey, P. N. Ciesielski, L. M. Wheeler, P. Schulz, L. Y. Lin, M. C. Beard and J. M. Luther, *Sci. Adv.*, 2017, **3**, eaao4204.
- 1337 V. Gonzalez-Pedro, X. Xu, I. Mora-Serj and J. Bisquert, *ACS Nano*, 2010, **4**, 5783–5790.



- 1338 H. Dong, F. Xu, Z. Sun, X. Wu, Q. Zhang, Y. Zhai, X. D. Tan, L. He, T. Xu, Z. Zhang and X. Duan, *Nat. Nanotechnol.*, 2019, **14**, 950–956.
- 1339 M. C. Hanna and A. J. Nozik, *J. Appl. Phys.*, 2006, **100**, 074510.
- 1340 K. Singh and O. Voznyy, *Chem*, 2019, **5**, 1692–1694.
- 1341 R. H. Gilmore, Y. Liu, W. Shcherbakov-Wu, N. S. Dahod, E. M. Lee, M. C. Weidman, H. Li, J. Jean, V. Bulović, A. P. Willard and J. C. Grossman, *Matter*, 2019, **1**, 250–265.
- 1342 Y. B. Zhao, M. Liu, O. Voznyy, B. Sun, P. C. Li, H. Kung, O. Ouellette, M. J. Choi, Z. H. Lu, F. P. G. de Arquer and E. H. Sargent, *Nano Energy*, 2019, **63**, 103876.
- 1343 H. Zhang, W. Fang, Y. Zhong and Q. Zhao, *J. Colloid. Interface Sci.*, 2019, **547**, 267–274.
- 1344 P. Guyot-Sionnest, *J. Phys. Chem. Lett.*, 2012, **3**, 1169–1175.
- 1345 D. Zhitomirsky, O. Voznyy, L. Levina, S. Hoogland, K. W. Kemp, A. H. Ip, S. M. Thon and E. H. Sargent, *Nat. Commun.*, 2014, **5**, 3803.
- 1346 A. H. Ip, A. Kiani, I. J. Kramer, O. Voznyy, H. F. Movahed, L. Levina, M. M. Adachi, S. Hoogland and E. H. Sargent, *ACS Nano*, 2015, **9**, 8833–8842.
- 1347 H. Li, D. Zhitomirsky, S. Dave and J. C. Grossman, *ACS Nano*, 2016, **10**, 606–614.
- 1348 A. H. Ip, S. M. Thon, S. Hoogland, O. Voznyy, D. Zhitomirsky, R. Debnath, L. Levina, L. R. Rollny, G. H. Carey, A. Fischer, K. W. Kemp, I. J. Kramer, Z. Ning, A. J. Labelle, K. W. Chou, A. Amassian and E. H. Sargent, *Nat. Nanotechnol.*, 2012, **7**, 577.
- 1349 J. Tang, K. W. Kemp, S. Hoogland, K. S. Jeong, H. Liu, L. Levina, M. Furukawa, X. Wang, R. Debnath, D. Cha and K. W. Chou, *Nat. Mater.*, 2011, **10**, 765–771.
- 1350 X. Lan, O. Voznyy, A. Kiani, F. P. García de Arquer, A. S. Abbas, G. H. Kim, M. Liu, Z. Yang, G. Walters, J. Xu and M. Yuan, *Adv. Mater.*, 2016, **28**, 299–304.
- 1351 F. Huang, Q. Zhang, B. Xu, J. Hou, Y. Wang, R. C. Massé, S. Peng, J. Liu and G. Cao, *J. Mater. Chem. A*, 2016, **4**, 14773–14780.
- 1352 F. Huang, J. Hou, Q. Zhang, Y. Wang, R. C. Massé, S. Peng, H. Wang, J. Liu and G. Cao, *Nano Energy*, 2016, **26**, 114–122.
- 1353 F. Huang, J. Hou, H. Wang, H. Tang, Z. Liu, L. Zhang, Q. Zhang, S. Peng, J. Liu and G. Cao, *Nano Energy*, 2017, **32**, 433–440.
- 1354 Y. S. Lee, C. V. Gopi, A. E. Reddy, C. Nagaraju and H. J. Kim, *New J. Chem.*, 2017, **41**, 1914–1917.
- 1355 K. Zhao, Z. Pan, I. Mora-Seró, E. Cánovas, H. Wang, Y. Song, X. Gong, J. Wang, M. Bonn, J. Bisquert and X. Zhong, *J. Am. Chem. Soc.*, 2015, **137**, 5602–5609.
- 1356 G. S. Selopal, H. Zhao, Z. M. Wang and F. Rosei, *Adv. Funct. Mater.*, 2020, **30**, 1908762.
- 1357 D. C. Neo, C. Cheng, S. D. Stranks, S. M. Fairclough, J. S. Kim, A. I. Kirkland, J. M. Smith, H. J. Snaith, H. E. Assender and A. A. Watt, *Chem. Mater.*, 2014, **26**, 4004–4013.
- 1358 J. Yang, J. Wang, K. Zhao, T. Izuishi, Y. Li, Q. Shen and X. Zhong, *J. Phys. Chem. C*, 2015, **119**, 28800–28808.
- 1359 M. J. Speirs, D. M. Balazs, H. H. Fang, L. H. Lai, L. Protesescu, M. V. Kovalenko and M. A. Loi, *J. Mater. Chem. A*, 2015, **3**, 1450–1457.
- 1360 Y. Nandan and M. S. Mehata, *Sci. Rep.*, 2019, **9**, 1–11.
- 1361 J. Wang, I. Mora-Seró, Z. Pan, K. Zhao, H. Zhang, Y. Feng, G. Yang, X. Zhong and J. Bisquert, *J. Am. Chem. Soc.*, 2013, **135**, 15913–15922.
- 1362 A. Sahasrabudhe and S. Bhattacharyya, *Chem. Mater.*, 2015, **27**, 4848–4859.
- 1363 S. Jiao, Q. Shen, I. Mora-Sero, J. Wang, Z. Pan, K. Zhao, Y. Kuga, X. Zhong and J. Bisquert, *ACS Nano*, 2015, **9**, 908–915.
- 1364 Z. Yang, J. Z. Fan, A. H. Proppe, F. P. G. De Arquer, D. Rossouw, O. Voznyy, X. Lan, M. Liu, G. Walters, R. Quintero-Bermudez, B. Sun, S. Hoogland, G. A. Botton, S. O. Kelley and E. H. Sargent, *Nat. Commun.*, 2017, **8**, 1325.
- 1365 A. K. Rath, F. Pelayo Garcia de Arquer, A. Stavrinadis, T. Lasanta, M. Bernechea, S. L. Diedenhofen and G. Konstantatos, *Adv. Mater.*, 2014, **26**, 4741–4747.
- 1366 P. G. Linares, C. D. Farmer, E. Antolín, S. Chakrabarti, A. M. Sánchez, T. Ben, S. I. Molina, C. R. Stanley, A. Martí and A. Luque, *Energy Procedia*, 2010, **2**, 133–141.
- 1367 L. Yue, H. Rao, J. Du, Z. Pan, J. Yu and X. Zhong, *RSC Adv.*, 2018, **8**, 3637–3645.
- 1368 M. Liu, O. Voznyy, R. Sabatini, F. P. G. de Arquer, R. Munir, A. H. Balawi, X. Lan, F. Fan, G. Walters, A. R. Kirmani and S. Hoogland, *Nat. Mater.*, 2017, **16**, 258–263.
- 1369 L. Protesescu, S. Yakunin, M. I. Bodnarchuk, F. Krieg, R. Caputo, C. H. Hendon, R. X. Yang, A. Walsh and M. V. Kovalenko, *Nano Lett.*, 2015, **15**, 3692–3696.
- 1370 J. Du, Z. Du, J.-S. Hu, Z. Pan, Q. Shen, J. Sun, D. Long, H. Dong, L. Sun, X. Zhong and L.-J. Wan, *J. Am. Chem. Soc.*, 2016, **138**, 4201–4209.
- 1371 M. M. Tavakoli, H. Aashuri, A. Simchi and Z. Fan, *Phys. Chem. Chem. Phys.*, 2015, **17**, 24412–24419.
- 1372 Y. Zhu, X. Meng, H. Cui, S. Jia, J. Dong, J. Zheng, J. Zhao, Z. Wang, L. Li, L. Zhang and Z. Zhu, *ACS Appl. Mater. Interfaces*, 2014, **6**, 13833–13840.
- 1373 H. Kim and K. Yong, *Phys. Chem. Chem. Phys.*, 2013, **15**, 2109–2116.
- 1374 S. R. Tulsani, A. K. Rath and D. J. Late, *Nanoscale Adv.*, 2019, **1**, 1387–1394.
- 1375 I. Kriegel, M. Ghini, S. Bellani, K. Zhang, A. W. Jansons, B. M. Crockett, K. M. Koskela, E. S. Barnard, E. Penzo, J. E. Hutchison and J. A. Robinson, *J. Phys. Chem. C*, 2020, **124**, 8000–8007.
- 1376 Z. Jin, M. Yuan, H. Li, H. Yang, Q. Zhou, H. Liu, X. Lan, M. Liu, J. Wang, E. H. Sargent and Y. Li, *Adv. Funct. Mater.*, 2016, **26**, 5284–5289.
- 1377 M. Shanmugam, N. Jain, R. Jacobs-Gedrim, Y. Xu and B. Yu, *Appl. Phys. Lett.*, 2013, **103**, 243904.
- 1378 C. Zhang, Y. Li, P. Zhang, M. Qiu, X. Jiang and X. H. Zhang, *Sol. Energy Mater. Sol. Cells*, 2019, **189**, 11–20.
- 1379 M. Wright and A. Uddin, *Sol. Energy Mater. Sol. Cells*, 2012, **107**, 87–111.
- 1380 T. Xu and Q. Qiao, *Energy Environ. Sci.*, 2011, **4**, 2700–2720.
- 1381 F. Gao, S. Ren and J. Wang, *Energy Environ. Sci.*, 2013, **6**, 2020–2040.



- 1382 Y. Zhou, M. Eck and M. Krüger, *Energy Environ. Sci.*, 2010, **3**, 1851–1864.
- 1383 J. Chandrasekaran, D. Nithyaprakash, K. B. Ajjan, S. Maruthamuthu, D. Manoharan and S. Kumar, *Renewable Sustainable Energy Rev.*, 2011, **15**, 1228–1238.
- 1384 R. Liu, *Materials*, 2014, **7**, 2747–2771.
- 1385 S. Ren, L. Y. Chang, S. K. Lim, J. Zhao, M. Smith, N. Zhao, V. Bulovic, M. Bawendi and S. Gradecak, *Nano Lett.*, 2011, **11**, 3998–4002.
- 1386 P. Guyot-Sionnest and M. A. Hines, *Appl. Phys. Lett.*, 1998, **72**, 686–688.
- 1387 Y. Wang, K. Liu, P. Mukherjee, D. A. Hines, P. Santra, H. Y. Shen, P. Kamat and D. H. Waldeck, *Phys. Chem. Chem. Phys.*, 2014, **16**, 5066–5070.
- 1388 A. Grupp, P. Ehrenreich, J. Kalb, A. Budweg, L. Schmidt-Mende and D. Brida, *J. Phys. Chem. Lett.*, 2017, **8**, 4858–4864.
- 1389 C. Krause, R. Miranti, F. Witt, J. Neumann, D. Fenske, J. Parisi and H. Borchert, *Sol. Energy Mater. Sol. Cells*, 2014, **124**, 241–246.
- 1390 A. Lefrançois, B. Luszczynska, B. Pepin-Donat, C. Lombard, B. Bouthinon, J. M. Verilhac, M. Gromova, J. Faure-Vincent, S. Pouget, F. Chandezon and S. Sadki, *Sci. Rep.*, 2015, **5**, 1–8.
- 1391 X. Jiang, F. Chen, Q. Weiming, Q. Yan, Y. Nan, H. Xu, L. Yang and H. Chen, *Sol. Energy Mater. Sol. Cells*, 2010, **94**, 2223–2229.
- 1392 N. C. Greenham, X. Peng and A. P. Alivisatos, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1996, **54**, 17628–17637.
- 1393 W. U. Huynh, J. J. Dittmer and A. P. Alivisatos, *Science*, 2002, **295**, 2425–2427.
- 1394 W. U. Huynh, J. J. Dittmer, N. Teclemariam, D. J. Milliron, A. P. Alivisatos and K. W. Barnham, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2003, **67**, 115326.
- 1395 D. Celik, M. Krueger, C. Veit, H. F. Schleiermacher, B. Zimmermann, S. Allard, I. Dumsch, U. Scherf, F. Rauscher and P. Niyamakom, *Sol. Energy Mater. Sol. Cells*, 2012, **98**, 433–440.
- 1396 B. Li, J. M. Kim and G. A. Amaratunga, *Isr. J. Chem.*, 2019, **59**, 720–728.
- 1397 S. Ren, L.-Y. Chang, S.-K. Lim, J. Zhao, M. Smith, N. Zhao, V. Bulović, M. Bawendi and S. Gradecak, *Nano Lett.*, 2011, **11**, 3998–4002.
- 1398 T. Zhang, S. Iqbal, X. Y. Zhang, W. Wu, D. Su and H. L. Zhou, *Sol. Energy Mater. Sol. Cells*, 2020, **204**, 110245.
- 1399 Y. Zhang, W. Cui, Y. Zhu, F. Zu, L. Liao, S. T. Lee and B. Sun, *Energy Environ. Sci.*, 2015, **8**, 297–302.
- 1400 D.-Y. Khan, *J. Phys. D: Appl. Phys.*, 2019, **52**, 503002.
- 1401 S. S. Yoon and D. Y. Khang, *Adv. Energy Mater.*, 2018, **8**, 1702655.
- 1402 J. He, P. Gao, Z. Yang, J. Yu, W. Yu, Y. Zhang, J. Sheng, J. Ye, J. C. Amine and Y. Cui, *Adv. Mater.*, 2017, **29**, 1606321.
- 1403 D. Zielke, A. Pazidis, F. Werner and J. Schmidt, *Sol. Energy Mater. Sol. Cells*, 2014, **131**, 110–116.
- 1404 J. Hossain, Q. Liu, T. Miura, K. Kasahara, D. Harada, R. Ishikawa, K. Ueno and H. Shirai, *ACS Appl. Mater. Interfaces*, 2016, **8**, 31926–31934.
- 1405 S. Jäckle, M. Liebhaber, J. Niederhausen, M. Büchele, R. Félix, R. G. Wilks, M. Bär, K. Lips and S. Christiansen, *ACS Appl. Mater. Interfaces*, 2016, **8**, 8841–8848.
- 1406 S. H. Tsai, H. C. Chang, H. H. Wang, S. Y. Chen, C. A. Lin, S. A. Chen, Y. L. Chueh and J. H. He, *ACS Nano*, 2011, **5**, 9501.
- 1407 W. W. He, K. J. Wu, K. Wang, T. F. Shi, L. Wu, S. X. Li, D. Y. Teng and C. H. Ye, *Sci. Rep.*, 2014, **4**, 3715.
- 1408 A. F. Madsuha, C. Van Pham, M. Eck, M. Neukom and M. Krueger, *J. Nanomater.*, 2019, **2019**, 6095863.
- 1409 D. H. Shin, S. H. Shin, S. Kim and S. H. Choi, *Nanotechnology*, 2019, **31**, 095202.
- 1410 Y. Qin, Y. Cheng, L. Jiang, X. Jin, M. Li, X. Luo, G. Liao, T. Wei and Q. Li, *ACS Sustainable Chem. Eng.*, 2015, **3**, 637.
- 1411 J. H. Lee, D. W. Shin, V. G. Makotchenko, A. S. Nazarov, V. E. Fedorov, Y. H. Kim, J.-Y. Choi, J. M. Kim and J.-B. Yoo, *Adv. Mater.*, 2009, **21**, 4383–4387.
- 1412 S. Ye, A. R. Rathmell, Z. Chen, I. E. Stewart and B. J. Wiley, *Adv. Mater.*, 2014, **26**, 6670–6687.
- 1413 <http://www.cambrios.com> (accessed on June 2021).
- 1414 <https://www.cheaptubes.com/product-category/single-walled-carbon-nanotubes/> (accessed on June 2021).
- 1415 <http://www.kintec.hk/> (accessed on June 2021).
- 1416 U.S. Geological Survey, Mineral Commodity Summaries, Indium, U.S. Department of the Interior, Washington, D.C., USA, 2014, pp. 74.
- 1417 K. Montazeri, M. Currie, L. Verger, P. Dianat, M. W. Barsoum and B. Nabet, *Adv. Mater.*, 2019, **31**, 1903271.
- 1418 Y. Ma, B. Li and S. Yang, *Mater. Chem. Front.*, 2018, **2**, 456–467.

