Chemical Science



EDGE ARTICLE

View Article Online
View Journal | View Issue



Cite this: Chem. Sci., 2021, 12, 4450

dll publication charges for this article have been paid for by the Royal Society of Chemistry

Received 22nd August 2020 Accepted 1st February 2021

DOI: 10.1039/d0sc04647g

rsc.li/chemical-science

Optimal water concentration for aqueous Li⁺ intercalation in vanadyl phosphate[†]

Dan Sun,^a Masashi Okubo obab and Atsuo Yamada obab

Development of high-performance aqueous batteries is an important goal for energy sustainability owing to their environmental benignity and low fabrication costs. Although a layered vanadyl phosphate is one of the most-studied host materials for intercalation electrodes with organic electrolytes, little attention has been paid to its use in aqueous Li⁺ systems because of its excessive dissolution in water. Herein, by controlling the water concentration, we demonstrate the stable operation of a layered vanadyl phosphate electrode in an aqueous Li⁺ electrolyte. The combination of experimental analyses and density functional theory calculations reveals that reversible (de)lithiation occurs between dehydrated phases, which can only exist in an optimal water concentration.

Introduction

Lithium-ion batteries (LIBs) dominate the battery market for portable electronics and electric vehicles owing to their long lifetime, high efficiency, and high energy densities. However, LIBs are comprised of flammable and costly organic electrolytes, which unexceptionally accompany both safety hazards and high fabrication costs.1 Batteries that utilize aqueous electrolytes are expected to provide more operational safety, affordability, high power, and environmental benignity, all of which are favorable for large-scale stationary systems and electric vehicle operations.^{2,3} Although the intrinsically narrow electrochemical stability window for water as an electrolyte solvent (~1.23 V) imposed severe limitations on any practical applications of aqueous batteries, novel strategies involving highly concentrated aqueous electrolytes have achieved much wider electrochemical potential windows (>3 V), thereby paving a path for the development of more practical aqueous batteries.4-8 Importantly, by exploiting a specialized solution structure without free water,9-14 highly concentrated aqueous electrolytes can also provide unexpected environments for electrode materials that have been considered 'useless' in conventional dilute aqueous electrolytes.15

The selection criteria of electrode materials for aqueous batteries are (i) suitable redox potential, (ii) durability against water, (iii) no side reactions, (iv) good reversibility, and (v) low cost. Fig. S1† lists selected electrode materials that are

 $VOPO_4 \cdot 2H_2O$ possesses a bilayer structure where a $VOPO_4$ layer is composed of corner-sharing VO_6 octahedra and PO_4 tetrahedra, with a layer distance of 7.25 Å along the c axis, as illustrated in Fig. 1a. When $VOPO_4 \cdot nH_2O$ is immersed in liquids that possess high water concentration $c(H_2O)$ (e.g., pure

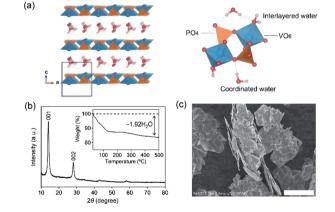


Fig. 1 (a) Crystal structure of VOPO $_4 \cdot nH_2O$. V (dark cyan), P (orange), O (red), and H (gray) atoms are shown. (b) Powder X-ray diffraction pattern and (c) scanning electron microscopy image of VOPO $_4 \cdot nH_2O$. The inset in (b) is the thermal gravimetric analysis profile of VOPO $_4 \cdot nH_2O$.

potentially compatible with aqueous electrolytes. Among them, for instance, hydrated vanadyl phosphate (VOPO $_4 \cdot nH_2O$, Fig. 1a) is a versatile layered host for intercalation chemistry, which has been ascertained using various organic electrolyte systems. ^{16–21} However, except for a few very recent reports of its application to aqueous H^+/Zn^{2+} batteries, ^{22,23} VOPO $_4 \cdot nH_2O$ has rarely been considered promising in aqueous systems, due simply to dissolution and decomposition of VOPO $_4 \cdot nH_2O$ in aqueous electrolytes.

^aDepartment of Chemical System Engineering, School of Engineering, The University of Tokyo, Hongo 7-3-1, Bunkyo-ku, Tokyo 113-8656, Japan. E-mail: yamada@chemsys.t. u-tokyo.ac.jp

^bElemental Strategy Initiative for Catalysts & Batteries (ESICB), Kyoto University, Nishikyo-ku, Kyoto 615-8510, Japan

 $[\]dagger$ Electronic supplementary information (ESI) available. See DOI: 10.1039/d0sc04647g

Edge Article Chemical Science

water or dilute aqueous solutions), surface vanadium atoms are readily coordinated by the water to form soluble vanadium aguo complexes. Furthermore, high-concentration water is prone to intercalate into an interlayer space to exfoliate VOPO4 layers, accelerating the dissolution process. Alternatively, an extremely low-c(H2O) environment (e.g., highly concentrated aqueous solutions) is expected to desorb interlayer water between VOPO₄ layers. Since interlayer water plays an important role in both structural integrity and ion diffusion, the intercalation chemistry may be largely altered via the control of $c(H_2O)$ of aqueous electrolytes for achieving reversible lithium-ion (de)intercalation in VOPO₄·nH₂O. Herein, we demonstrate the stable charge/ discharge operation of VOPO4·nH2O through accurate control of $c(H_2O)$ in aqueous Li⁺ electrolytes.

Results and discussion

VOPO₄·nH₂O was synthesized by refluxing V₂O₅ and H₃PO₄,²⁴ and the resulting powder was dried under vacuum overnight at 80 °C. The powder X-ray diffraction (XRD) pattern (Fig. 1b) corresponds to tetragonal VOPO4 · nH2O, and a 001 diffraction at $2\theta \approx 14^{\circ}$ indicates an interlayer distance of 7.35 Å. The thermogravimetric (TG) analysis (inset of Fig. 1b) reveals a water content per formula unit of n = 1.92. The scanning electron microscopy image (Fig. 1c) shows a lamellar morphology with a lateral size ranging from 10 to 100 μ m.

The dissolution durability of VOPO₄·nH₂O was tested using aqueous Li⁺ electrolytes (Fig. 2a). After immersing VOPO₄·nH₂O in aqueous electrolytes at various Li⁺: H₂O ratios for 30 days, the color of the dilute electrolyte (Li^+ : $H_2O = 1:50$, high $c(H_2O)$) changed to orange, while concentrated electrolytes (e.g., $Li^+: H_2O = 1: 4$, low $c(H_2O)$ remained transparent, indicating

effective suppression of vanadium ion dissolution by lowering $c(H_2O)$.

Cyclic voltammetry (CV) was conducted to evaluate the electrochemical properties of VOPO4·nH2O under various $c(H_2O)$ conditions (Fig. 2b-f). The CV curves for the dilute aqueous electrolyte (Li⁺: $H_2O = 1:50$, high $c(H_2O)$) (Fig. 2b) show severe decay of current flow with repeating CV cycles. The decay of current flow coincides with the change in the electrolyte color to orange, arising from the dissolution of vanadium in a high-c(H₂O) environment. In contrast, upon increasing the salt concentration (lowering $c(H_2O)$) to a Li⁺: H_2O ratio of 1: 4, intense multiple current flows gradually emerge with minimal polarization, indicating reversible (de)lithiation without parasitic reactions/dissolution. However, when further lowering $c(H_2O)$ to a Li⁺: H_2O ratio of 1: 2.5, the cyclic voltammetry (CV) curve shows broad cathodic/anodic current flows with large polarization (Fig. 2f), which indicates sluggish (de)lithiation of $VOPO_4 \cdot nH_2O$ in an environment of overly low $c(H_2O)$. Electrochemical impedance spectroscopy (Fig. S2†) shows the specific increase of both series resistance and charge-transfer resistance specifically when the Li+: H2O ratio changes from 1:4 to 1:2.5. Presumably, the low ionic conductivity of the highly concentrated aqueous electrolyte increases the series resistance while the strong coulombic attraction between Li⁺ and TFSI⁻ (contact-ion pair) increases the charge-transfer resistance, both of which cause the sluggish (de)lithiation of VOPO₄·nH₂O.¹⁴ Therefore, an optimal- $c(H_2O)$ environment (Li⁺: $H_2O = 1:4$) is required for reversible (de)lithiation of VOPO4·nH2O in aqueous systems.

Fig. 3a-c show the galvanostatic charge/discharge curves of $VOPO_4 \cdot nH_2O$ in various $c(H_2O)$ environments at a specific current of 1 A g^{-1} . The delivered capacity with a high- $c(H_2O)$

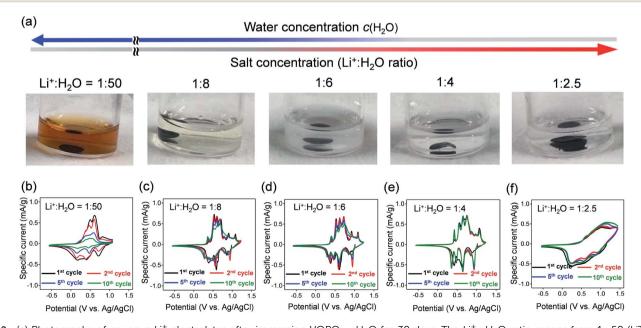


Fig. 2 (a) Photographs of aqueous Li⁺ electrolytes after immersing VOPO₄·nH₂O for 30 days. The Li⁺: H₂O ratio ranges from 1:50 (LiTFSI/ $50H_2O$), 1:8 (LiTFSI/ $8H_2O$), 1:6 (LiTFSI/ $6H_2O$), 1:4 (LiTFSI/ $4H_2O$) to 1:2.5 (water-in-salt, LiTFSI/ $2.5H_2O$). (b-f) Cyclic voltammetry curves of $VOPO_4 \cdot nH_2O$ in aqueous Li⁺ electrolytes at various Li⁺: H_2O ratios at a scan rate of 0.5 mV s⁻¹.

Li+:H₂O = 1:50 1.5- Li+:H₂O = 1:8 1.5 ° 0.5 \$ 0.5 0.0 0.0 ₫-0.5 200th 50th 5th 1s 15th 0 40 80 120 40 80 120 Capacity (mAh/g) Capacity (mAh/q) (d) (c) Li+:H2O = 1:4 150 Ag/AgCI) 1.0 Li⁺:H₂O = 1:4 o.5 جُ 0.0 lgia Li+:H2O = 1:8 -0.5 Li+:H2O = 1:50 80 120 100 Capacity (mAh/g)

Chemical Science

Fig. 3 Charge/discharge curves of VOPO $_4\cdot H_2O$ electrodes with aqueous Li $^+$ electrolytes. The Li $^+$: H_2O ratios are (a) 1:50 (LiTFSI/50 H_2O), (b) 1:8 (LiTFSI/8 H_2O), and (c) 1:4 (LiTFSI/4 H_2O), respectively. The specific current is 1 A g $^{-1}$. (d) Capacity retention during 200 charge/discharge cycles.

aqueous electrolyte (Fig. 3a) drastically decreases upon cycling, while the potential polarization increases, presumably because of the vanadium dissolution. Upon gradually lowering $c(H_2O)$ to an optimal range (Li⁺: H₂O = 1:4), the potential profiles exhibit distinct multiple plateaus without substantial polarization, indicating highly reversible (de)lithiation (Fig. 3b and c). However, when further lowering $c(H_2O)$ to $Li^+: H_2O = 1: 2.5$, the polarization between lithiation/delithiation significantly increases to reduce the reversible capacity to approximately 85 mA h g^{-1} (Fig. S3†). These results are consistent with the CV results (Fig. 2). The reversible capacity of 118 mA h g⁻¹ in the first cycle (Li⁺: H₂O = 1:4) corresponds to 0.8 Li⁺ intercalation per formula unit. The reversible reduction/oxidation of vanadium (V⁵⁺/V⁴⁺) upon charge/discharge, which was confirmed by V K-edge X-ray absorption spectroscopy (Fig. S4†), supports the occurrence of reversible (de)lithiation of VOPO₄·nH₂O. Furthermore, owing to the optimal-c(H₂O) environment, 80% of the initial capacity is retained after 200 cycles (Fig. 3d), which is much higher than that for a high-c(H2O) aqueous electrolyte (7%).

To clarify the phase diagram of $\text{Li}_x \text{VOPO}_4 \cdot n \text{H}_2 \text{O}$ in the optimal $c(\text{H}_2 \text{O})$ environment, in situ XRD experiments were conducted (Fig. 4a–c). Before immersion in the optimal- $c(\text{H}_2 \text{O})$ electrolyte, $\text{VOPO}_4 \cdot n \text{H}_2 \text{O}$ in a composite electrode possesses an interlayer distance of 7.2 Å. The calculated interlayer distance of $\text{VOPO}_4 \cdot 2 \text{H}_2 \text{O}$ (7.25 Å, Fig. S5 and Table S1†) agrees with the experimental value, and the water content of $\text{VOPO}_4 \cdot n \text{H}_2 \text{O}$ in a pristine electrode is estimated as $n \approx 2$, which is in good agreement with the TG result (the inset of Fig. 1b). However, the in situ XRD pattern for $\text{VOPO}_4 \cdot n \text{H}_2 \text{O}$ immersed in a LiTFSI/4H₂O electrolyte shows the shift of 001 diffraction to a higher diffraction angle (Fig. 4a), indicating the decrease of the interlayer distance to 6.2 Å. This value is consistent with the

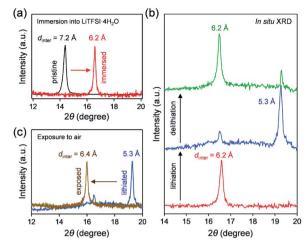


Fig. 4 Structural changes of $VOPO_4 \cdot nH_2O$ in LiTFSI/4H₂O. The 001 diffraction peak (a) before and after immersion in LiTFSI/4H₂O, (b) after lithiation and delithiation in LiTFSI/4H₂O, and (c) before and after exposure of a lithiated sample to the ambient atmosphere. d_{inter} denotes the interlayer distance.

calculated interlayer distance for VOPO₄·H₂O (6.16 Å, Fig. S5 and Table S1†). Therefore, the low- $c(H_2O)$ environment dehydrates VOPO₄·nH₂O to a monohydrate phase (n=1). Upon lithiation/delithiation, a new 001 diffraction, corresponding to an interlayer distance of 5.3 Å, emerges/diminishes at the expense of the original 001 diffraction (Fig. 4b), suggesting biphasic (de)lithiation. It is noteworthy that the lithiated/delithiated monohydrate phases are stable only in the optimal- $c(H_2O)$ environment; for instance, the lithiated phase immediately becomes hydrated to a dihydrate phase (n=2) after being exposed to the ambient atmosphere (Fig. 4c).

A phase diagram of $\text{Li}_x \text{VOPO}_4 \cdot n \text{H}_2 \text{O}$ in the optimal- $c(\text{H}_2 \text{O})$ environment is postulated based on the experimental and simulation results as schematized in Fig. 5. The equilibrium between interlayer water in $\text{VOPO}_4 \cdot n \text{H}_2 \text{O}$ and low-concentration water in concentrated aqueous electrolytes

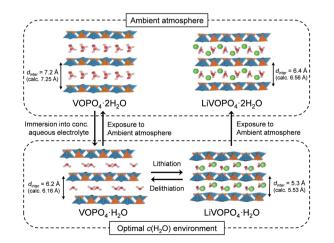


Fig. 5 Schematic illustration of the phase diagram of VOPO $_4 \cdot nH_2O$ in the optimal- $c(H_2O)$ environment.

drives dehydration of VOPO $_4 \cdot n H_2O$ to the monohydrate phase (n=1). Although exhibiting reversible Li⁺ (de)intercalation, the monohydrate phases can only be stabilized in a low- $c(H_2O)$ environment, and exposure to the ambient atmosphere immediately causes hydration to the dihydrate phase (n=2).

Conclusions

In summary, the stable operation of VOPO $_4 \cdot nH_2O$ electrodes in an optimal- $c(H_2O)$ environment was successfully demonstrated. The reversible (de)lithiation occurs specifically in monohydrate phases, which are only stable in the optimal- $c(H_2O)$ environment. This study provides novel insights into the reaction mechanism and phase diagram of VOPO $_4 \cdot nH_2O$ in a low- $c(H_2O)$ environment, and more importantly points to research opportunities to enrich aqueous ion intercalation chemistry by controlling water concentration.

Methods

 $VOPO_4 \cdot nH_2O$ was synthesized *via* a reflux method: V_2O_5 (6 g), H_2O (144 mL) and H_3PO_4 (82%, 57.75 g) at 125 °C for 16 h. After cooling to room temperature, the resulting yellow precipitate was collected by centrifugation and washed three times with water and acetone. Thereafter, the powder was dried under vacuum overnight at 80 °C.

X-ray diffraction patterns were recorded on a Bruker AXS D8 Advance X-ray diffractometer using Co K α radiation. Microstructure analyses were performed using a scanning electron microscope (Hitachi, S-4800) at a beam accelerating voltage of 5 kV. The oxidation states of the samples were measured by V K-edge XANES at the beamline 8B of Photon Factory (PF), High Energy Accelerator Research Organization (KEK) Tsukuba, Japan. The crystal water content of the as-synthesized VOPO $_4$ - $_1$ - $_1$ - $_2$ O sample was confirmed by TG (NETZSCH, STA2500).

VOPO₄·nH₂O electrodes were fabricated by grinding a mixture containing VOPO₄·nH₂O, carbon black (super P) and polytetrafluoroethylene (PTFE) in a weight ratio of 75:10:15 for 20 min, and then it was rolled into an electrode film using a rolling machine with a fixed gap of 250 µm. For the preparaaqueous electrolytes, lithium bis-(trifluoromethanesulfonyl)imide (LiTFSI) was dissolved ultrapure water as LiTFSI·nH₂O (n = 2.5, 4, 6, 8,and 50). The electrochemical performance of VOPO4·nH2O electrodes was evaluated using a three-electrode system (Ag/AgCl and active carbon as the reference and counter electrodes, respectively). CR2032-type coin cells were assembled to measure the galvanostatic charge/discharge properties of the electrodes. The cell consists of a VOPO₄·nH₂O electrode, active carbon anode and glass fiber separator (GF/F, Whatman). Electrochemical impedance spectroscopy (VMP3 potentiostat, Biologic) was performed at the open circuit potential with an amplitude of 10 mV in the frequency range of 10 mHz to 200 kHz.

First-principles calculations were performed using the Vienna *Ab initio* Simulation Package (VASP),²⁵ based on density functional theory (DFT).^{26,27} The exchange–correlation energy is calculated using general gradient approximation (GGA) with the

Perdue–Burke–Ernzerhof (PBE) exchange–correlation functional. Furthermore, in our calculations, Hubbard U corrections (GGA + U) were adopted with U-J=3.1 for vanadium. The effect of van der Waals interactions was estimated and implemented in the optimized exchange van der Waals functional B86b of the Becke (optB86b vdW) functional. Phase wave cutoff energy was 580 eV. The convergence condition for the energy is 10^{-4} eV, and the structures were relaxed until the force on each atom was less than 0.01 eV Å $^{-1}$. Spin polarization was considered in all calculations. The k-point meshes of $7 \times 7 \times 7$ and $14 \times 14 \times 14$ in the Monkhorst–Pack sampling scheme were used for geometry optimization and electronic self-consistent computation, respectively.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by the Ministry of Education, Culture, Sports, Science and Technology (MEXT), Japan; Grant-in-Aid for Specially Promoted Research No. 15H05701 and the "Elemental Strategy Initiative for Catalysis and Batteries" (ESICB). M. O. was financially supported by JSPS KAKENHI, Grant Numbers 19H05816, 18K19124, and 18H03924. The structure drawing was generated using VESTA.³²

Notes and references

- 1 M. R. Palacín and A. de Guibert, Science, 2016, 351, 1253292.
- 2 W. Li, J. R. Dahn and D. S. Wainwright, Science, 1994, 264, 1115-1118.
- 3 W. Tang, Y. S. Zhu, Y. Y. Hou, L. L. Liu, Y. P. Wu, K. P. Loh, H. P. Zhang and K. Zhu, *Energy Environ. Sci.*, 2013, **6**, 2093–2104.
- 4 L. Suo, O. Borodin, T. Gao, M. Olguin, J. Ho, X. Fan, C. Luo, C. Wang and K. Xu, *Science*, 2015, 350, 938–943.
- 5 Y. Yamada, K. Usui, K. Sodeyama, S. Ko, Y. Tateyama and A. Yamada, *Nat. Energy*, 2016, **1**, 16129.
- 6 C. Y. Yang, J. Chen, T. T. Qing, X. L. Fan, W. Sun, A. von Cresce, M. S. Ding, O. Borodin, J. Vatamanu, M. A. Schroeder, N. Eidson, C. S. Wang and K. Xu, *Joule*, 2017, 1, 122–132.
- 7 C. Y. Yang, J. Chen, X. Ji, T. P. Pollard, X. J. Lu, C. J. Sun, S. Hou, Q. Liu, C. M. Liu, T. T. Qing, Y. Q. Wang, O. Borodin, Y. Ren, K. Xu and C. S. Wang, *Nature*, 2019, 569, 245.
- 8 L. W. Jiang, Y. X. Lu, C. L. Zhao, L. L. Liu, J. N. Zhang, Q. Q. Zhang, X. Shen, J. M. Zhao, X. Q. Yu, H. Li, X. J. Huang, L. Q. Chen and Y. S. Hu, *Nat. Energy*, 2019, 4, 495–503.
- 9 J. Vatamanu and O. Borodin, J. Phys. Chem. Lett., 2017, 8, 4362–4367.
- O. Borodin, L. M. Suo, M. Gobet, X. M. Ren, F. Wang,
 A. Faraone, J. Peng, M. Olguin, M. Schroeder, M. S. Ding,
 E. Gobrogge, A. V. Cresce, S. Munoz, J. A. Dura,

This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.

Open Access Article. Published on 11 2021. Downloaded on 07/11/25 11:55:57

Chemical Science

- S. Greenbaum, C. S. Wang and K. Xu, ACS Nano, 2017, 11, 10462–10471.
- 11 K. Miyazaki, N. Takenaka, E. Watanabe, S. Iizuka, Y. Yamada, Y. Tateyama and A. Yamada, *J. Phys. Chem. Lett.*, 2019, **10**, 6301–6305.
- 12 N. Takenaka, T. Inagaki, T. Shimada, Y. Yamada, M. Nagaoka and A. Yamada, *J. Chem. Phys.*, 2020, **152**, 124706.
- 13 K. Kim, Y. Ando, A. Sugahara, S. Ko, Y. Yamada, M. Otani, M. Okubo and A. Yamada, *Chem. Mater.*, 2019, **31**, 5190– 5196.
- 14 K. Kim, M. Okubo and A. Yamada, *J. Electrochem. Soc.*, 2019, **166**, A3739–A3744.
- 15 A. Yamada, Joule, 2018, 2, 371-372.
- 16 A. J. Jacobson, J. W. Johnson, J. F. Brody, J. C. Scanlon and J. T. Lewandowski, *Inorg. Chem.*, 1985, 24, 1782–1787.
- 17 J. Gaubicher, T. Le Mercier, Y. Chabre, J. Angenault and M. Quarton, *J. Electrochem. Soc.*, 1999, **146**, 4375.
- 18 N. Dupre, J. Gaubicher, T. Le Mercier, G. Wallez, J. Angenault and M. Ouarton, *Solid State Ionics*, 2001, **140**, 209–221.
- 19 Y. N. Song, P. Y. Zavalij and M. S. Whittingham, *J. Electrochem. Soc.*, 2005, **152**, A721–A728.
- 20 M. S. Whittingham, Y. N. Song, S. Lutta, P. Y. Zavalij and N. A. Chernova, *J. Mater. Chem.*, 2005, 15, 3362–3379.

- 21 Y. Zhu, L. L. Peng, D. H. Chen and G. H. Yu, *Nano Lett.*, 2016, **16**, 742–747.
- 22 H. Y. Shi, Y. Song, Z. M. Qin, C. C. Li, D. Guo, X. X. Liu and X. Q. Sun, *Angew. Chem.*, *Int. Ed.*, 2019, **58**, 16057–16061.
- 23 F. Wan, Y. Zhang, L. L. Zhang, D. B. Liu, C. D. Wang, L. Song, Z. Q. Niu and J. Chen, *Angew. Chem.*, *Int. Ed.*, 2019, 58, 7062–7067.
- 24 J. Hyoung, J. W. Heo, M. S. Chae and S. T. Hong, ChemSusChem, 2019, 12, 1069–1075.
- 25 G. Kresse and J. Hafner, Phys. Rev. B: Condens. Matter Mater. Phys., 1994, 49, 14251-14269.
- 26 P. Hohenberg and W. Kohn, *Phys. Rev. B: Solid State*, 1964, **136**, B864–B871.
- 27 W. Kohn and L. J. Sham, Phys. Rev., 1965, 140, 1133.
- 28 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, 77, 3865–3868.
- 29 J. Klimes, D. R. Bowler and A. Michaelides, *J. Phys.: Condens. Matter*, 2010, **22**, 022201.
- 30 J. Klimes, D. R. Bowler and A. Michaelides, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2011, **83**, 195131.
- 31 H. J. Monkhorst and J. D. Pack, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1976, **13**, 5188–5192.
- 32 K. Momma and F. Izumi, J. Appl. Crystallogr., 2008, 41, 653-658.