
Volume 1 Number 3 May 2023 Pages 173-324

EES Catalysis

rsc.li/EESCatalysis



ISSN 2753-801X

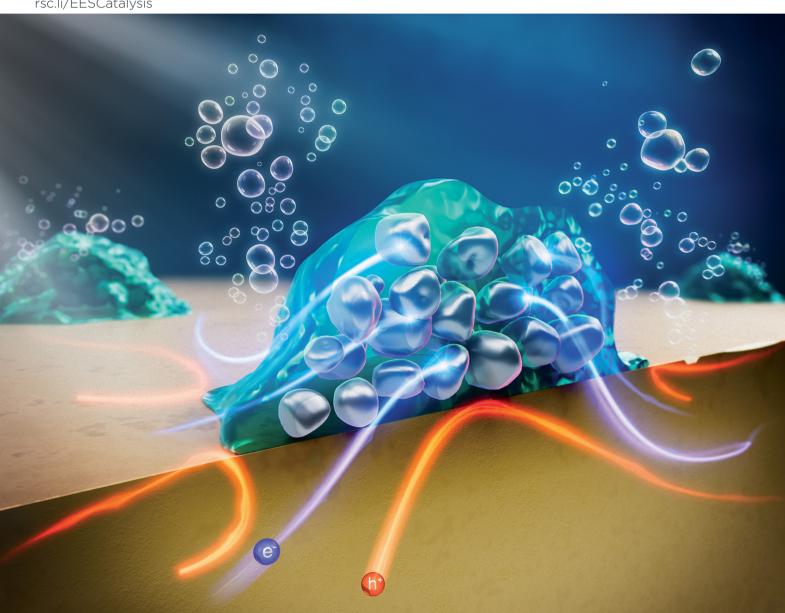

PAPER

Ryu Abe et al.

An unexplored role of the CrO, shell in an elaborated Rh/CrO, core-shell cocatalyst for photocatalytic water splitting: a selective electron transport pathway from semiconductors to core metals, boosting charge separation and H₂ evolution

EES Catalysis



View Article Online **PAPER**



Cite this: EES Catal., 2023,

Rh/CrO_x core-shell cocatalyst for photocatalytic water splitting: a selective electron transport pathway from semiconductors to core metals, boosting charge separation and H₂ evolution†

An unexplored role of the CrO_x shell in an elaborated

Tetsu Kotani,‡a Kanta Ogawa, 🗓 ‡a Hajime Suzuki, 🗓 Kosaku Kato, 🗓 b Osamu Tomita, Da Akira Yamakata Db and Ryu Abe +

A core-shell structured Rh/CrO_x cocatalyst has endowed various semiconductors with high efficiency in water-splitting photocatalysis, where thin CrO_x layers on Rh have been assumed to be physical blockers of O_2 to the metal surface to suppress unfavorable reverse reactions (e.g., catalytic H_2O formation from H_2 and O_2). Herein, we propose another unexplored but favorable function of CrO_x layers: a selective electron transport pathway from photocatalysts to the Rh core boosting charge separation and H₂ production. The subsequent loading of CrO_x layers onto Rh increased the rate of visible light H_2 evolution of a Bi₄NbO₈Cl photocatalyst, even in a half reaction with a hole scavenger where O₂ does not evolve. Transient absorption spectroscopy revealed that the CrO_x layer increases the electron path from Bi₄NbO₈Cl to Rh. Importantly, the highest H₂-evolution activity was obtained by simultaneous photodeposition using Cr^{III} and Rh^{III} precursors, which had not yet been examined. In this sample, Rh nanoparticles were enclosed by an amorphous CrOx shell, where Rh particles were less directly attached to the semiconductor. Therein, CrO_x inserted between Bi₄NbO₈Cl and Rh effectively suppresses undesirable hole transfer from Bi₄NbO₈Cl to Rh, while such hole transfer partially occurs when they are in direct contact. These results indicated that CrO_x functions as a selective electron transport pathway and improves the H₂ evolution activity. Although the development strategy of cocatalysts has so far focused on surface redox reactions, this study offers a new approach for the design of highly efficient cocatalysts based on the carrier transfer process, especially at semiconductor-cocatalyst interfaces.

Received 20th December 2022, Accepted 15th March 2023

DOI: 10.1039/d2ey00109h

rsc.li/eescatalysis

Broader context

Water splitting using a semiconductor photocatalyst enables clean hydrogen production from solar energy. Light irradiation excites electrons and holes in a photocatalyst. After their migration toward the surface of the photocatalyst, they participate in reduction and oxidation at reaction sites. Therefore, not only semiconductor photo-absorbers themselves, but also creating effective reaction sites on their surface is essential. Such a role can be played by "co-catalysts" on photocatalysts, the functions of which are generally (1) capturing either of photoexcited carriers from photocatalysts and (2) catalyzing redox reactions on the surface of photocatalysts. Although vast knowledge in electrocatalysis can be employed for the latter function, a versatile strategy has not yet been established for the former one. Here, we reveal that CrO_x in the Rh/CrO_x core-shell type cocatalyst helps in electron transfer from photocatalysts to the reaction sites (Rh). Rh/Cr₂O₃ is a widely used hydrogen evolution reaction cocatalyst in overall water splitting, where CrO_x has been considered to be a physical blocker of O₂ to the metal surface to suppress reverse reactions. We propose another function of CrO_x layers: a selective electron-transport pathway from photocatalysts to Rh, boosting charge separation and H2 production. This study offers a new approach for designing cocatalysts based on the carrier transfer process.

‡ T. K. and K. O. contributed equally to this work.

Introduction

Highly efficient photocatalytic water splitting inevitably requires not only an efficient semiconductor photo-absorber but also effective cocatalysts. 1-5 In general, cocatalysts loaded on semiconductor photocatalysts play two crucial roles: (1) capturing

^a Department of Energy and Hydrocarbon Chemistry, Graduate School of Engineering, Kyoto University, Nishikyo-ku, Kyoto, 615-8510, Japan. E-mail: ryu-abe@scl.kyoto-u.ac.jp

^b Graduate School of Natural Science and Technology, Okayama University, 3-1-1 Tsushima-naka, Kita-ku, Okayama, 700-8530, Japan

[†] Electronic supplementary information (ESI) available: SEM and TEM images, photocatalytic activity, and TA spectroscopy data. See DOI: https://doi.org/10. 1039/d2ev00109h

Paper photoexcited carriers (either electrons or holes ideally) from the from photocatalysts to the Rh core (i.e., reduction site), based on

photocatalysts and (2) reducing the activation energy of target redox reactions on the surface of photocatalysts. 6 In terms of the latter role, vast knowledge accumulated in electrochemical catalysis for the hydrogen evolution reaction (HER) and the oxygen evolution reaction (OER) has provided us with useful principles for designing effective cocatalyst materials (e.g., Pt for the HER and IrO₂ for the OER). However, in terms of the former role, a versatile strategy has not yet been established for cocatalysts to capture photoexcited carriers selectively because metal-semiconductor interfacial charge transfer consists of highly complex processes.^{8,9} Actually, even the most commonly used Pt cocatalyst captures photogenerated holes as well as photoexcited electrons in some cases, which causes undesirable charge recombination on Pt. 10-13 Therefore, photocatalytic water splitting systems with high efficiencies have been achieved based on the specially designed photocatalyst particles, where HER and OER cocatalysts are loaded on different crystal facets selectively by leveraging the photocatalytic deposition technique. Specifically, the Al-doped SrTiO₃ particle, which is synthesized using a flux method, possesses facet-dependent redox properties, and the photoexcited electrons accumulate on the {100} facet. Thus, it reduces metal cations to produce an HER cocatalyst (i.e., Rh/Cr₂O₃) on that facet, while the photogenerated holes accumulate on the {110} facet, producing an OER cocatalyst oxidatively (i.e., CoOOH) on it. Therefore, HER and OER cocatalysts selectively capture the photoexcited carriers that are desirable for photocatalytic water splitting. However, this strategy cannot be applied to other systems unless the photocatalyst material possesses a built-in and/or facetdependent charge separation ability (e.g., decahedral-shaped BiVO₄¹⁴).

The abovementioned Rh/Cr₂O₃ cocatalyst with a core-shell structure is one of the most widely used HER cocatalysts for achieving overall water splitting (i.e., simultaneous evolution of H₂ and O₂) on various photocatalyst materials owing to its excellent resistance to reverse reactions. 4,15,16 Unfavorable reactions involving O2 molecules, such as re-reduction of O2 and/or catalytic formation of H2O from H2 and O2 on conventional metallic HER cocatalysts (e.g., Rh and Pt), are one of the major issues in photocatalytic water splitting. Domen et al. demonstrated that a thin layer of Cr2O3·nH2O (denoted hereafter as CrO_r for brevity) coated on Rh (or Pt) effectively suppresses unfavorable reverse reactions on metal species because the layer is permeable to H⁺ but not to O₂, preventing O₂ molecules from reaching the metal surface.¹⁷

Although the vital role of the CrO_x shell as a physical blocker of O2 molecules has gained broad acceptance, we have noticed unaccountable results through our attempt to apply this Rh/ CrO_x cocatalyst to a layered oxyhalide Bi₄NbO₈Cl photocatalyst possessing appropriate properties for visible-light watersplitting. 18 Specifically, the subsequent loading of CrO_x onto Rh increases the rate of H₂ evolution on Bi₄NbO₈Cl in the presence of methanol as a sacrificial electron donor, where O2 does not evolve. In this study, we reveal an unexplored but favorable function of CrOx layers as a selective electron transport pathway

the results of varied Rh/CrO_x-type cocatalysts loaded on Bi₄NbO₈Cl, which were characterized by X-ray absorption near edge structure spectroscopy, X-ray photoelectron spectroscopy, transmission electron microscopy, and time-resolved spectroscopy.

Results and discussion

Photodeposition of Rh and CrO_r on Bi₄NbO₈Cl

Bi₄NbO₈Cl was synthesized using a flux method (Fig. S1, ESI†).19 Rh and Cr species were loaded on Bi₄NbO₈Cl via photodeposition using Na₃RhCl₆, Cr(NO₃)₃·9H₂O (Cr^{III}), and K₂CrO₄ (Cr^{VI}) as precursors. Notably, the conventional coreshell Rh/CrO_r cocatalysts were prepared mostly *via* stepwise photoreduction by photoexcited electrons, where Rh^{III} species (i.e., Na₃RhCl₆) were first reduced to form core Rh metal particles on the photocatalyst surface, and then CrVI species (K₂CrO₄) were reduced to Cr^{III} species by the electrons that accumulate on the Rh to form a shell on the Rh surface. It has been suggested that the shell layers formed on Rh mainly consist of a mixture of Cr₂O₃·nH₂O, while we herein describe them as CrO_x for simplicity, as in previous reports.²⁰ In addition to the high-valent CrVI precursor, we employed another precursor, Cr(NO₃)₃, containing low-valent (Cr^{III}) species. This is based on the expectation that the hydroxide ions (OH⁻) produced via the photocatalytic reduction of NO3- on Rh $(NO_3^- + H_2O + 2e^- \rightarrow NO_2^- + 2OH^-)$ can react with the Cr^{III} species to produce Cr(OH)3, finally forming CrOx-like species on the surface of the Rh core, as demonstrated in the coating of photocatalyst surface with CrO_x-like layers.²¹ The samples prepared via the stepwise method using Cr^{III} and Cr^{VI} will be hereafter denoted as Rh/Cr^{III} and Rh/Cr^{VI}, respectively. Herein, we also employed simultaneous deposition in which the photocatalyst particles were irradiated in a solution containing both Rh and Cr precursors (denoted as $Rh + Cr^{III}$ or $Rh + Cr^{VI}$). To the best of our knowledge, simultaneous deposition using CrIII as a precursor has not been investigated so far, while that with Cr^{VI} has been reported.22

Fig. 1 shows the Rh-K and Cr-K edge XANES spectra of the prepared samples. All the samples, except for Rh + Cr^{VI}, were confirmed to consist of the Rh metal species based on a comparison with the spectrum of the Rh metal foil. The spectrum of the Rh + CrVI sample resembles that of the reference Rh2O3, indicating the insufficient reduction of the Rh precursor by photoexcited electrons. This is probably due to the preferential reduction of Cr^{VI} (CrO₄²⁻ + 5H⁺ +3e⁻ ≠ $Cr(OH)_3 + H_2O$; $E^{\circ} = 1.386 \text{ V}$). The Cr-K spectra of all prepared samples were in good agreement with that of the reference Cr2O3. nH₂O (Fig. 1b) sample, as well as with previous data on CrO_x loaded GaN:ZnO.17,23 The EXAFS spectra further supported this conclusion (Fig. S2, ESI†). A trivalent Cr species is also observed by the X-ray photoelectron spectroscopy (XPS) analysis (Fig. S3, ESI†).

As shown in Fig. 2a, Rh particles were deposited as agglomerates with a size of approximately 20 nm when Rh was solely loaded on Bi₄NbO₈Cl; the lattice fringes ensured the zero-valent

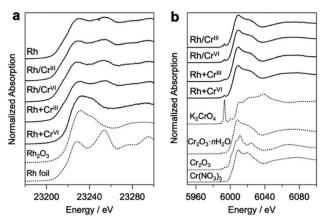


Fig. 1 (a) Rh-K and (b) Cr-K edge XANES spectra of Rh and Cr-loaded Bi₄NbO₈Cl prepared via stepwise (Rh/Cr^{III}, Rh/Cr^{VI}) and simultaneous deposition (Rh + Cr^{III}, Rh + Cr^{VI}). The reference samples are shown as dotted lines. Cr₂O₃·nH₂O was obtained via a precipitation reaction where NaOH was added to a Cr(NO₃)₃ solution.

state of Rh (Fig. S4, ESI†). Stepwise loading of the Cr precursor (Rh/CrIII and Rh/CrVI) formed an amorphous CrO_r layer (Fig. 2b and c) while maintaining the morphology and size of the Rh core. HAADF-STEM and EDX elemental mapping images confirmed the Rh/Cr core/shell structure (Fig. S5 and S6, ESI†). In stark contrast, the simultaneous deposition of the CrIII precursor (Rh + CrIII) provided differently shaped particles, where Rh of a few nanometer size was enclosed by an amorphous CrO_x shell (Fig. 2d-f and Fig. S7, ESI†). In each case, an easier reduction reaction on Rh than on the bare surface of Bi₄NbO₈Cl may contribute to CrO_x growth around Rh nanoparticles. Although some large particles were also observed (Fig. S8, ESI†), their number was small (less than 5.2% of the observed 200 particles). As for Rh + CrVI, only amorphous particles were deposited (Fig. S4, ESI†), which may be Rh^{III}-Cr^{III} mixed-oxides by considering the XANES spectra (Fig. 1a). 22,24

Impact of the CrO_r shell on the H₂ evolution activity of the Rhloaded Bi₄NbO₈Cl photocatalyst

H₂ evolution activities of the prepared samples were evaluated in an aqueous methanol solution (MeOH aq.) where the photoexcited electrons and holes are expected to react with water (or H⁺) and methanol, respectively. Fig. 3 shows the time courses of H₂ evolution on various samples under visible light irradiation ($\lambda > 400$ nm). The first noteworthy fact is that the coating of Rh with the CrO_x shell enhanced H₂ evolution; the Rh/Cr^{III} and Rh/ CrVI samples showed higher rates than Rh. The sample with CrO_x randomly deposited via the impregnation method instead of the photodeposition method showed a lower H2 evolution activity, which supports the function of the CrO_x layer on Rh (Fig. S9, ESI†). The second and most important finding of this study is that the Rh + Cr^{III} sample prepared *via* the unexplored simultaneous photodeposition of Rh^{III} and Cr^{III} precursors showed a significantly higher activity than the Rh-solely loaded and other CrO_x-coated samples. The negligible activity of Rh + CrVI prepared via simultaneous photodeposition of RhIII and

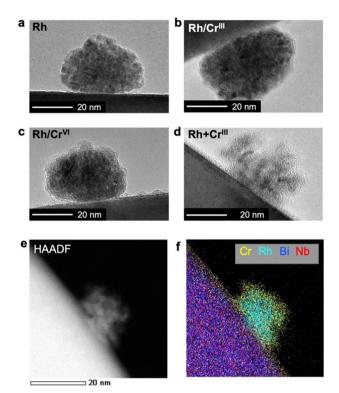


Fig. 2 HR-TEM images of cocatalysts loaded on (a) Rh, (b) Rh/Cr^{III}, (c) Rh/Cr^{VI}, and (d) Rh + Cr^{III} samples. (e) HAADF-STEM and (f) EDX elemental mapping images of the Rh + CrIII sample.

CrVI can be due to the insufficient reduction of the RhIII precursor, as indicated by the Rh K-edge XANES spectra (see Fig. 1).

The enhancement in the H₂-evolution reaction by CrO_x coating on Rh cannot be explained by the widely accepted role of the CrO_x shell as a physical blocker of O₂ molecules because O2 evolution should not take place in the presence of an efficient hole scavenger, methanol. One possible factor is the deactivation of the Rh metal surface by some intermediates generated from methanol, such as formaldehyde, as suggested in the case of the Pt cocatalyst loaded on TiO2. 25 However, H2 evolution on the Rh-loaded sample remained unchanged even in the presence of formaldehyde (Fig. S10, ESI†) in MeOH (aq.), which eliminates this possibility. The Bi₄NbO₈Cl sample loaded solely with CrO_x species (via photodeposition of the Cr^{VI} precursor) did not show detectable H₂ evolution from MeOH (aq.) under visible light irradiation (Fig. S11, ESI†), indicating negligible activity of CrO_x as an HER cocatalyst. ^{20,26} In addition, no H₂ was generated over Rh-loaded Cr₂O₃·nH₂O (i.e., in the absence of the Bi₄NbO₈Cl photocatalyst, see Fig. S12, ESI†), confirming the negligible activity of CrOx itself as a semiconductor photocatalyst under the present reaction conditions. The promotion of H₂ evolution from MeOH (aq.) by CrO_xcoating on Rh (prepared via simultaneous photodeposition of Rh^{III} and Cr^{III} precursors) was also observed on a conventional water-splitting photocatalyst SrTiO3 under UV light irradiation (Fig. 6), which demonstrates that this unexplored effect of the CrO_x shell is not specific to the Bi₄NbO₈Cl photocatalyst.

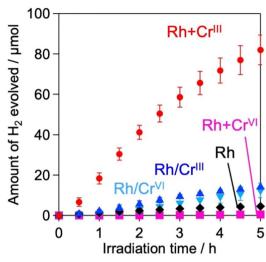


Fig. 3 Time courses of H₂ evolution of Rh (black), Rh/Cr^{III} (blue), Rh/Cr^{VI} (light blue), Rh + Cr^{III}, (red), and Rh + Cr^{VI} (pink) samples. The reactions were conducted in an aqueous methanol solution (20 vol%, 250 mL) under visible light irradiation ($\lambda > 400$ nm). Error bars signify the standard deviation.

Previous studies have reported enhanced H2 evolution from MeOH (aq.) by CrO_x shells on Rh for GaN:ZnO and SrTiO₃, while the detailed mechanism for enhancement has not been discussed. 17,27 These facts strongly suggest the presence of a previously unknown function of the CrO_r shell in enhancing H₂ evolution (i.e., reduction of H⁺ and/or water), in addition to its function as a physical blocker.

Spectroscopic elucidation of the unexplored function of the CrO_v shell

Based on these results and previous reports that CrO_x does not to promote the catalytic HER, 20,26 we focused on the effect of the loaded CrO_x on the charge carrier (either electrons or holes) transfer process rather than the catalytic process in photocatalysis. 20,26 We employed transient absorption (TA) spectroscopy²⁸⁻³⁰ to evaluate the effect of CrOx on the carrier dynamics between a photocatalyst (Bi₄NbO₈Cl) and its catalytic site (Rh). Fig. 4a shows the TA spectra of bare Bi₄NbO₈Cl, where bandgap excitation induces two absorption increases in the infrared (IR) (2000 cm⁻¹) and visible (20 800 cm⁻¹) regions. Referring to previous results (e.g., TiO₂, ^{31–33} α -Fe₂O₃³⁴ and LaTiO₂N²⁸), the IR features have been attributed to photogenerated free electrons in the conduction band (CB) and/or shallowly trapped electrons, ^{35,36} while the visible features have been associated with photogenerated holes.^{29,30}

Fig. 4b and c show the decay kinetics of the IR (2000 cm⁻¹ for electrons) and visible (20 800 cm⁻¹ for holes) regions, respectively, for the various samples. Compared to the bare Bi₄NbO₈Cl, the sole loading of Rh metal species decreased the signal intensity of electrons but increased that of holes, indicating the preferential capture of photoexcited electrons by Rh, as reported previously.13 The deposition of CrOx shells on the Rh-loaded $\rm Bi_4NbO_8Cl~(Rh/Cr^{III}~and~Rh/Cr^{VI})$ further decreased the electron signal but had little impact on the hole signal. Given the fact that the CrOx shells on the pre-loaded Rh

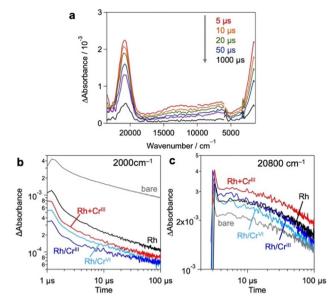


Fig. 4 (a) TA spectra of bare Bi₄NbO₈Cl after excitation. (b and c) Decay kinetics of the transient absorption in the μ -second regions measured at (b) 2000 cm $^{-1}$ and (c) 20800 cm $^{-1}$ in N₂ (20 torr). The samples were excited by UV laser pulses (355 nm).

increased the rate of H₂ evolution despite the inertness of CrO_x for the HER, 20,26 it appears that CrO_x captures the photoexcited electrons from Bi₄NbO₈Cl, transfers them to the Rh core, and consequently increases the number of electrons for the HER. More importantly, in the Rh + CrIII sample, which shows the highest H2 evolution activity, the signal of holes was further increased compared to that of the Rh-loaded sample, whereas the electron signal was decreased as with the case of Rh/CrIII and Rh/CrVI. This phenomenon suggests that the charge separation between the holes on Bi₄NbO₈Cl and the electrons on Rh was further improved by the CrO_r species loaded via the unexplored simultaneous photodeposition of the Rh^{III} and Cr^{III} precursors, which is consistent with the highest H₂ evolution activity of this sample. In other words, the function of CrO_x, selective electron transfer from Bi₄NbO₈Cl to Rh, was more apparent in this sample. A similar tendency was also observed in an earlier process on a pico-second scale (Fig. S13, ESI†).

The electron-selective capturing ability of the CrO_x shell was further supported by the TA values of the bare and CrO_x-loaded Bi₄NbO₈Cl samples. As shown in Fig. S15 (ESI†), CrO_x loading on the bare Bi₄NbO₈Cl surface significantly decreased the IR signal but increased the visible signal. These results on TA measurements strongly suggest that the CrO_x species can selectively capture photoexcited electrons from Bi₄NbO₈Cl, prolonging the lifetime of the holes by promoting the spatial separation of electrons and holes.

Mechanism for significant enhancement in H₂ production on the Rh/CrOx cocatalyst

Based on the above results (physicochemical properties, photocatalytic activity, and carrier dynamics), we now propose a previously unknown function of the CrOx shell as an electron **EES Catalysis**

transport layer between the semiconductor and the Rh core, as illustrated in Fig. 5.

In the Rh/Cr^{III} and Rh/Cr^{VI} samples, where CrO_r was subsequently photodeposited on the pre-loaded Rh, the CrO_r layers, as well as the Rh directly attached to Bi₄NbO₈Cl, capture the photoexcited electrons from Bi₄NbO₈Cl, serving as an electron path between Bi₄NbO₈Cl and Rh (Fig. 5a). Therefore, the CrO_x layer on Rh facilitated electron transfer to Rh, increasing the number of electrons participating in H⁺ reduction on Rh, enhancing H2 evolution. Notably, a much higher H2 evolution rate was observed for the Rh + CrIII sample, where most of the Rh nanoparticles were enclosed by an amorphous CrO_x shell, and the contact area between Rh and Bi₄NbO₈Cl was much smaller than that of the other samples (Fig. 2 and Fig. S8, ESI†). Given the TA results indicating the electron-selective capturing ability of CrOx, the CrOx intermediate between Bi4NbO8Cl and Rh in Rh + Cr^{III} selectively passed electrons, thus boosting H₂ evolution (Fig. 5b). Although undesirable hole transfer from Bi₄NbO₈Cl to Rh partially occurs when they are in direct contact with each other, as in the case of Pt, 10-13 the insertion of the electron-selective pathway of CrO_r effectively suppresses this hole transfer and therefore the problematic charge recombination at the semiconductor-metal interfaces. The function of CrO_r as an electron-selective pathway was further supported by the enhanced H₂ evolution on the sample where CrO_x was first deposited on Bi₄NbO₈Cl followed by the Rh species (Fig. S16, ESI†). The sample showed a much higher activity than the Rhloaded one despite the incomplete reduction to metal and agglomerated morphology of the Rh species, indicating the effectiveness of CrO_x for improving the carrier transfer process.

The function of the CrO_x shell as a "selective" electron transport layer is similar to those employed in solar cells to suppress charge recombination.³⁷ Indeed, some chromium oxide species have been reported to serve as an electron transport layer between a semiconductor photo-absorber (e.g.,

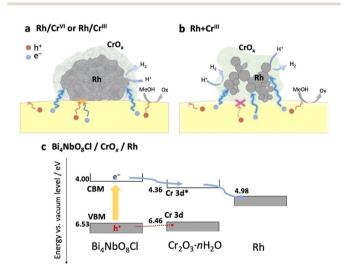


Fig. 5 Schematic of the role of CrO_x in the carrier transfer process from the semiconductor photocatalyst to Rh in (a) Rh/Cr^{III} (or Rh/Cr^{VI}) and (b) Rh + Cr^{III}. (c) Energy level diagram for Bi₄NbO₈Cl, Cr₂O₃·nH₂O, and Rh.

lead-halide perovskite solar cells) and an electrode (e.g., fluorine-doped tin oxide (FTO) and Ag substrates).38,39 Generally, the function of an electron transport layer can be explained based on the band alignment among three components (i.e., photo-absorber, electron transport layer, and conductive electrode). The band levels of the CrO_r species were estimated using a combination of diffuse reflectance spectroscopy and photoelectron yield spectroscopy (Fig. S17, ESI†). Cr₂O₃·nH₂O particles were prepared via a precipitation method in which OH was added to the solution containing Cr3+ ions to imitate the photodeposition process of CrO_x from Cr³⁺ on Bi₄NbO₈Cl. The Cr-K edge XANES of the sample confirmed the formation of almost the same species as that loaded on Bi₄NbO₈Cl. Fig. 5c shows the estimated band alignments for Bi₄NbO₈Cl, Cr₂O₃· nH_2O , and Rh. The CBM (Cr-3d*)⁴⁰ position of Cr₂O₃· nH_2O was favorable for receiving electrons generated in the CBM of Bi₄NbO₈Cl and injecting them into Rh. Given the band alignment, the holes, not only electrons, can transfer to Cr₂O₃·nH₂O. However, the driving force (energy difference between the VBM and Cr-3d) is much smaller than that for the electrons (from the CBM to Cr-3d*), which is probably one of the origins of the preferred electron transfer in addition to other factors such as donor or acceptor density of the present CrOx species. In other words, the driving force of hole transfer (work function difference) from Bi₄NbO₈Cl to Rh (about 1.55 eV) can be reduced to 0.07 eV by introducing the CrO_r layer, which can suppress the undesirable hole transfer from the photocatalyst to Rh.

From these results, we conclude that CrO_x functions as a selective electron transport layer, promoting charge separation between the photocatalyst and noble metal reaction sites, thus boosting H₂ evolution. The significant improvement in H₂ evolution indicates that the CrO_x layers formed via the present procedure (i.e., simultaneous photodeposition) possess substantial permeability to H+ (or other related species such as H₃O⁺), as proposed in previous reports on conventional Rh/ CrO_x cocatalysts. 4,15,16 Another important question arises: whether the CrO_x layers formed via the present procedure can function as a physical blocker against O2 molecules, which will be discussed later.

Applicability of the CrO_x layers formed via simultaneous deposition to other systems

The significant impact of CrO_r layers on H₂ evolution was also confirmed for other metal cores and semiconductors, as it was not specific to the combination of the Rh core and Bi₄NbO₈Cl. As for metal cores, we have previously revealed that conventional Pt cocatalysts cannot boost H2 production on Bi4NbO8Cl because Pt captures both electrons and holes, acting as a recombination center¹³ as shown in Fig. S18 (ESI†). When Pt and Cr species were simultaneously loaded on Bi₄NbO₈Cl (Pt + Cr^{III}), most of the Pt particles were encapsulated by amorphous CrO_x (Fig. S19 and S20, ESI†), as in the case of Rh + Cr^{III} . The Pt + Cr^{III} sample showed much improved H₂ evolution compared to the Pt sample, which strongly suggests that the CrO_x layer also helps selective electron transfer from Bi₄NbO₈Cl to Pt (Fig. S21, ESI†).

Paper

C H₂ evolution rate / µmol h⁻¹ Bi₄NbO₈CI 150 evolution rate / µmol h⁻¹ H₂ evolution rate / μmol h⁻¹ SrTiO₃ TiO₂ 20 100 40 10 50 20 Rh+Crill Rh+CrIII Rh Rh+Crll

Fig. 6 Effect of co-deposition of CrO_x with Rh on the photocatalytic activity of (a) Bi_4NbO_8Cl ($\lambda > 400$ nm), (b) $SrTiO_3$ ($\lambda > 300$ nm), and (c) rutile TiO_2 ($\lambda > 300$ nm).

The simultaneous photodeposition of CrO_x and Rh on SrTiO₃ (Rh + Cr^{III}) also provides a higher H₂ evolution rate from MeOH (aq.) compared to Rh-loaded SrTiO3 (Fig. S22, ESI†), whereas the enhancement was moderate compared to that of Bi₄NbO₈Cl (Fig. 6 and Table S3, ESI†). In contrast, the co-deposition of CrO_x significantly lowered the H₂ evolution rate of Rh-loaded rutile TiO₂ (Fig. S24, ESI†) from MeOH (aq.). This stark contrast may support the abovementioned electrontransfer mechanism. Since the CBM level of SrTiO₃ (ca. 4.2 eV against the vacuum level) is almost the same as that of Bi₄NbO₈Cl and higher than that of CrO_x, the electron transfer from SrTiO₃ to Rh through CrO_x layers can be rationalized (see Fig. S25, ESI†). On the other hand, the CBM of rutile TiO₂ is lower (ca. 4.37 eV against the vacuum level) than that of Bi₄NbO₈Cl and quite similar to that of CrO_x, making the driving force of the electron transfer through the conduction band of CrO_r almost negligible.

As noted in the Introduction, the main role of the CrO_x layer has been regarded as a physical blocker of O2 molecules to suppress reverse reactions such as water formation (from H₂ and O2) and O2 reduction on noble metal cocatalysts. To investigate the role of the CrOx layers prepared via simultaneous photodeposition (i.e., Rh + CrIII), overall water splitting was performed using the SrTiO3 photocatalyst. As shown in Fig. S26 (ESI†), while the Rh-loaded SrTiO₃ without CrO_x does not show stoichiometric water splitting due to the undesirable reaction with O₂ molecules on the exposed Rh,⁶ simultaneous CrO_x deposition provided stoichiometric water splitting, which confirms the role of the CrO_x shell as a physical blocker. Notably, the sample prepared using the present method (Rh + Cr^{III}) showed slightly higher photocatalytic activity than the sample prepared using the conventional method (Rh/CrVI). Unfortunately, we have not yet succeeded in splitting pure water into H2 and O2 using the Bi4NbO8Cl samples loaded with these Rh/CrO_x cocatalysts, probably because of the insufficient optimization of other factors such as the loading of an effective O₂-evolution cocatalyst, which will be our future work.

Conclusions

In summary, we demonstrated that CrO_x facilitates the transfer of photoexcited electrons from a photoeatalyst to a noble metal

reduction site. The CrO_x layer on the pre-loaded Rh served as an electron path, facilitating electron transfer from the Bi₄NbO₈Cl photocatalyst to Rh, which resulted in improved H2 evolution activity under visible light. Notably, when Rh and CrOx are loaded simultaneously via photodeposition using a Cr3+ precursor, CrO_r lies between Rh and Bi₄NbO₈Cl. Therein, the CrO_r layer passes only electrons to Rh, suppressing undesirable hole transfer to Rh, which further improves the activity. Thus far, the facilitation of surface reactions (e.g., the HER and OER) has mainly been investigated as a function of the cocatalysts. However, we revealed the crucial role of CrO_x in the carrier transfer process from the photocatalyst to the catalyst (reaction site). We believe that the precise control of the physicochemical properties of Cr species by doping,41 making solid solutions with other transition metal compounds, 40 and employing other ligands (anions)42,43 will reveal more detailed dynamics in the carrier transport process from photocatalysts to noble metals to suppress the undesirable charge recombination more effectively. Employing other semiconductors having appropriate band edge positions as electron transport layers will also be an effective choice. This study offers a new approach for designing cocatalysts based on their carrier-capturing abilities.

Experimental

Materials

Bi₂O₃ (99.99%), BiOCl (95.0%), Nb₂O₅ (99.9%), NaCl (99.5%), CsCl, methanol (99.8%), Rh₂O₃ (98.0%), K₂CrO₄ (99.0%), CrO₃(99.5%), H₂PtCl₆·6H₂O (99.9%), PtO₂ (98.0%), and BN were purchased from FUJIFILM Wako Pure Chemicals. Na₃RhCl₆·nH₂O (80.0%), Cr(NO₃)₃·9H₂O (98.0%), and Cr₂O₃ (98.5%) were purchased from Kanto Chemical. SrTiO₃ (99%) was purchased from Sigma-Aldrich. TiO₂ (rutile, 99.99%) was purchased from High Purity Chemicals. Formaldehyde solution (37%) was purchased from Nacalai Tesque. The compound described as Cr₂O₃·nH₂O was obtained from the precipitate formed by the addition of NaOH to the Cr(NO₃)₃ solution.

Synthesis of Bi₄NbO₈Cl using the flux method

 ${\rm Bi_4NbO_8Cl}$ was synthesized using the flux method, as reported in our previous work. Briefly, a stoichiometric mixture of ${\rm Bi_2O_3}$, BiOCl, and ${\rm Nb_2O_5}$ was mixed with flux (NaCl and CsCl in the molar ratio of 35:65) at 1 mol%. The mixture (25 g) was placed in a 30 mL alumina crucible, heated at a rate of 50 °C h⁻¹ to 650 °C, and held at the final temperature for 10 h. The product was naturally cooled to room temperature, thoroughly washed with distilled water, filtered, and air-dried. The obtained powder was confirmed to be ${\rm Bi_4NbO_8Cl}$ by X-ray diffraction (XRD).

Loading of the co-catalyst

The prepared Bi₄NbO₈Cl (0.2 g) was dispersed in an aqueous methanol solution (20 vol%, 250 mL). Depending on the preparation conditions, the Rh precursor (Na₃RhCl₆·*n*H₂O), Pt precursor (H₂PtCl₆·6H₂O), and/or Cr precursor (Cr(NO₃)₃·9H₂O

or K₂CrO₄) were added to the solution. The amount of precursor added was 1.0 wt% for Rh (or Pt) and 1.5 wt% for Cr as a metal cation (Fig. S20, ESI†). After degassing, the solution was irradiated with visible light ($\lambda > 400$ nm) for 5 h at room temperature under continuous stirring. Irradiation was conducted using a 300 W Xe lamp equipped with a CM1 cold mirror and an L-42 cutoff filter. The product was filtered, washed thoroughly with distilled water, and air-dried. Absorption spectroscopy ensured that precursors for the Rh were fully consumed during the PD process, while the loading amounts of Cr were approximately 0.6, 1.3, and 1.3 wt% for Rh/CrVI, Rh/

CrO_x was also loaded using the impregnation method. A certain amount of Rh/Bi₄NbO₈Cl powder was immersed in an aqueous solution containing Cr(NO₃)₃ (1.5 wt%). The suspension was evaporated under constant stirring until achieving complete dryness, followed by heating under an Ar flow at 150 °C.

Cr^{III}, and Rh + Cr^{III}, respectively (Fig. S28, ESI†).

Characterization

EES Catalysis

The prepared samples were studied by X-ray absorption fine structure (XAFS) spectroscopy, X-ray photoelectron spectroscopy (XPS), transmission electron microscopy (TEM), and scanning electron microscopy (SEM). XAFS measurements were carried out at the AR-NW10A, BL9C, and BL12C beamlines of the Photon Factory (High Energy Accelerator Research Organization, Tsukuba, Japan). The X-ray energy was varied using a Si(111) double-crystal monochromator. The reference samples were diluted in boron nitride, compressed to form pellets (except for Rh foil), and measured in the transmission mode. Cocatalyst-loaded samples were measured in fluorescence mode using a multichannel solid-state detector. XPS measurements were carried out with 5500MT (ULVAC-PHI) using Mg Ka as the X-ray source. The spectra were calibrated with the $4f_{7/2}$ peak (84.0 eV) of Au deposited on the sample surface using a magnetron sputtering device (MSP-1S). TEM and SEM were conducted using a JEM-2100F (JEOL) and an Nvision 40 (Zeiss), respectively.

Photocatalytic reaction

The photocatalytic reactions were performed in a closed circulation system. The sample (0.1 g) was dispersed in an aqueous methanol solution (20 vol%, 250 mL) in a Pyrex reaction vessel. After degassing, the solution was irradiated using a 300 W Xe lamp at room temperature with continuous stirring. In the case of Bi₄NbO₈Cl, the sample was irradiated (visible light ($\lambda > 400$ nm)) using a CM1 cold mirror and an L-42 cutoff filter. The evolved gases were analyzed using a gas chromatograph (GC-8A, SHIMADZU) with a thermal conductivity detector (TCD) using Ar as the carrier gas.

Transient absorption (TA) measurements

TA measurements were performed using a custom-built spectrometer as previously described. Briefly, for microsecond measurements, samples fixed on a CaF2 plate were excited by a 355 nm laser pulse (0.5 mJ pulse energy, 0.5-1 Hz repetition

rate). As a probe light, visible to near-IR light (25 000-6000 cm⁻¹) was irradiated from a halogen lamp and mid-IR light (6000-1000 cm⁻¹) was irradiated from the MoSi₂ coil. The transmitted or diffuse reflected probe light monochromated using a spectrometer was detected using Si, InGaAs, and MCT detectors in the visible, near-IR, and mid-IR regions, respectively. Picosecond measurements were performed using a Ti:sapphire laser system (Spectra-Physics, Solstice & TOPAS Prime; 90 fs duration; 500 Hz repetition rate). To excite the samples, 355 nm pulses (6 µJ pulse energy) were used. The probes 20 800 cm⁻¹ and 2000 cm⁻¹ were detected using a photomultiplier and an MCT detector, respectively. All the TA measurements were performed under N₂ (20 torr). The bare Bi₄NbO₈Cl sample used here was irradiated in a methanol solution in advance to obtain a light irradiation history similar to that of other photodeposited samples.

Author contributions

Tetsu Kotani: data curation, investigation, methodology visualization, and writing - original draft. Kanta Ogawa: conceptualization, investigation, methodology, and writing - original draft. Hajime Suzuki: writing - review & editing. Kosaku Kato: investigation. Osamu Tomita: investigation. Akira Yamakata: resources and data curation. Ryu Abe: resources, supervision, and writing - review & editing.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by the JST-CREST project, the JSPS KAKENHI Grant-in-Aid for Scientific Research (A) (JP20H00398), the JSPS KAKENHI Grant Number 17H06439 for Scientific Research on Innovative Areas "Innovations for Light-Energy Conversion (I4LEC)," the JSPS Research Fellowship (Grant Number 19J23357), and the JSPS Core-to-Core Program (JPJSCCA20200004). This work was also supported by the Iketani Science and Technology Foundation and the TEPCO Memorial Foundation. A part of this work was supported by the Advanced Research Infrastructure for Materials and Nanotechnology in Japan (JPMXP1222KU0026). We acknowledge Prof. Shunsuke Nozawa of KEK for his helpful support in XAFS measurement. We are also grateful to Takaaki Toriyama of Kyushu University for his helpful support in the STEM analysis.

Notes and references

- 1 R. Abe, Bull. Chem. Soc. Jpn., 2011, 84, 1000-1030.
- 2 M. R. Shaner, H. A. Atwater, N. S. Lewis and E. W. McFarland, Energy Environ. Sci., 2016, 9, 2354-2371.
- 3 R. Bala Chandran, S. Breen, Y. Shao, S. Ardo and A. Z. Weber, Energy Environ. Sci., 2018, 11, 115-135.

- 4 T. Takata, J. Jiang, Y. Sakata, M. Nakabayashi, N. Shibata, V. Nandal, K. Seki, T. Hisatomi and K. Domen, Nature, 2020, **581**, 411-414.
- 5 Y. Shang, T. Wang, Y. Xiao, Z. Dong, X. Li and B. Li, J. Alloys Compd., 2021, 875, 159998.
- 6 K. Maeda and K. Domen, Bull. Chem. Soc. Ipn., 2016, 89, 627-648.
- 7 A. Kudo and Y. Miseki, Chem. Soc. Rev., 2009, 38, 253-278.
- 8 V. Subramanian, E. E. Wolf and P. V. Kamat, J. Am. Chem. Soc., 2004, 126, 4943-4950.
- 9 K. Wu, H. Zhu, Z. Liu, W. Rodríguez-Córdoba and T. Lian, J. Am. Chem. Soc., 2012, 134, 10337-10340.
- 10 M. Yoshida, A. Yamakata, K. Takanabe, J. Kubota, M. Osawa and K. Domen, J. Am. Chem. Soc., 2009, 131, 13218-13219.
- 11 S. Schäfer, S. A. Wyrzgol, R. Caterino, A. Jentys, S. J. Schoell, M. Hävecker, A. Knop-Gericke, J. A. Lercher, I. D. Sharp and M. Stutzmann, J. Am. Chem. Soc., 2012, 134, 12528-12535.
- 12 F. Yan, Y. Wang, J. Zhang, Z. Lin, J. Zheng and F. Huang, ChemSusChem, 2014, 7, 101-104.
- 13 K. Ogawa, R. Sakamoto, C. Zhong, H. Suzuki, K. Kato, O. Tomita, K. Nakashima, A. Yamakata, T. Tachikawa, A. Saeki, H. Kageyama and R. Abe, Chem. Sci., 2022, 13, 3118-3128.
- 14 R. Li, F. Zhang, D. Wang, J. Yang, M. Li, J. Zhu, X. Zhou, H. Han and C. Li, Nat. Commun., 2013, 4, 1432.
- 15 Z. Wang, Y. Inoue, T. Hisatomi, R. Ishikawa, Q. Wang, T. Takata, S. Chen, N. Shibata, Y. Ikuhara and K. Domen, Nat. Catal., 2018, 1, 756-763.
- 16 Q. Wang, M. Nakabayashi, T. Hisatomi, S. Sun, S. Akiyama, Z. Wang, Z. Pan, X. Xiao, T. Watanabe, T. Yamada, N. Shibata, T. Takata and K. Domen, Nat. Mater., 2019, 18, 827-832.
- 17 K. Maeda, K. Teramura, D. Lu, N. Saito, Y. Inoue and K. Domen, J. Phys. Chem. C, 2007, 111, 7554-7560.
- 18 H. Fujito, H. Kunioku, D. Kato, H. Suzuki, M. Higashi, H. Kageyama and R. Abe, J. Am. Chem. Soc., 2016, 138, 2082-2085.
- 19 K. Ogawa, A. Nakada, H. Suzuki, O. Tomita, M. Higashi, A. Saeki, H. Kageyama and R. Abe, ACS Appl. Mater. Interfaces, 2019, 11, 5642-5650.
- 20 M. Qureshi, T. Shinagawa, N. Tsiapis and K. Takanabe, ACS Sustainable Chem. Eng., 2017, 5, 8079-8088.
- 21 S. Chu, R. T. Rashid, X. Liu and Z. Mi, Chem. Commun., 2019, 55, 6305-6308.
- 22 K. Maeda, D. Lu, K. Teramura and K. Domen, Energy Environ. Sci., 2010, 3, 471-478.
- 23 K. Maeda, N. Sakamoto, T. Ikeda, H. Ohtsuka, A. Xiong, D. Lu, M. Kanehara, T. Teranishi and K. Domen, Chem. -Eur. J., 2010, 16, 7750-7759.
- 24 K. Maeda, D. Lu, K. Teramura and K. Domen, J. Mater. Chem., 2008, 18, 3539.

- 25 H. Huang, J. Feng, S. Zhang, H. Zhang, X. Wang, T. Yu, C. Chen, Z. Yi, J. Ye, Z. Li and Z. Zou, Appl. Catal., B, 2020, 272, 118980.
- 26 M. Yoshida, K. Takanabe, K. Maeda, A. Ishikawa, J. Kubota, Y. Sakata, Y. Ikezawa and K. Domen, J. Phys. Chem. C, 2009, **113**, 10151-10157.
- 27 Y.-J. Cho, G. Moon, T. Kanazawa, K. Maeda and W. Choi, Chem. Commun., 2016, 52, 9636-9639.
- 28 A. Yamakata, M. Kawaguchi, N. Nishimura, T. Minegishi, J. Kubota and K. Domen, J. Phys. Chem. C, 2014, 118, 23897-23906.
- 29 J. Tang, J. R. Durrant and D. R. Klug, J. Am. Chem. Soc., 2008, 130, 13885-13891.
- 30 K. Murofushi, K. Ogawa, H. Suzuki, R. Sakamoto, O. Tomita, K. Kato, A. Yamakata, A. Saeki and R. Abe, J. Mater. Chem. A. 2021, 9, 11718-11725.
- 31 D. W. Bahnemann, M. Hilgendorff and R. Memming, J. Phys. Chem. B, 1997, 101, 4265-4275.
- 32 T. Yoshihara, R. Katoh, A. Furube, Y. Tamaki, M. Murai, K. Hara, S. Murata, H. Arakawa and M. Tachiya, I. Phys. Chem. B, 2004, 108, 3817-3823.
- 33 Y. Tamaki, A. Furube, M. Murai, K. Hara, R. Katoh and M. Tachiya, J. Am. Chem. Soc., 2006, 128, 416-417.
- 34 M. Barroso, C. A. Mesa, S. R. Pendlebury, A. J. Cowan, T. Hisatomi, K. Sivula, M. Grätzel, D. R. Klug and J. R. Durrant, Proc. Natl. Acad. Sci. U. S. A., 2012, 109, 15640-15645.
- 35 J. I. Pankove, Optical Processes in Semiconductors, Dover Publication, New York, 1975.
- 36 P. K. Basu, Theory of Optical Processes in Semiconductors, Oxford University Press, New York, 1997.
- 37 K. Wang, S. Olthof, W. S. Subhani, X. Jiang, Y. Cao, L. Duan, H. Wang, M. Du and S. (Frank) Liu, Nano Energy, 2020, 68, 104289.
- 38 S. Zheng, W. Li, T. Su, F. Xie, J. Chen, Z. Yang, Y. Zhang, S. Liu, M. P. Aldred, K. Y. Wong, J. Xu and Z. Chi, Sol. RRL, 2018, 2, 1700245.
- 39 J. Dong, J. Wu, J. Jia, X. He, Z. Lan, L. Fan, J. Lin and M. Huang, ChemSusChem, 2018, 11, 619-628.
- 40 Y. Wang, K. Lopata, S. A. Chambers, N. Govind and P. V. Sushko, J. Phys. Chem. C, 2013, 117, 25504-25512.
- 41 E. Arca, A. B. Kehoe, T. D. Veal, A. Shmeliov, D. O. Scanlon, C. Downing, D. Daly, D. Mullarkey, I. V. Shvets, V. Nicolosi and G. W. Watson, J. Mater. Chem. C, 2017, 5, 12610-12618.
- 42 S. Ohkoshi, K. Nakagawa, K. Tomono, K. Imoto, Y. Tsunobuchi and H. Tokoro, J. Am. Chem. Soc., 2010, 132, 6620-6621.
- 43 L. Lin, Z. Lin, J. Zhang, X. Cai, W. Lin, Z. Yu and X. Wang, Nat. Catal., 2020, 3, 649-655.