# **Materials Horizons**



### COMMUNICATION

View Article Online



Cite this: Mater. Horiz., 2023, 10.4270

Received 8th June 2023, Accepted 25th July 2023

DOI: 10.1039/d3mh00882g

rsc.li/materials-horizons

## Defect-stabilized and oxygen-coordinated iron single-atom sites facilitate hydrogen peroxide electrosynthesis†

Taotao Gao, ab Lu Qiu, bc Minghao Xie, d Zhaoyu Jin, pe Panpan Li the tand

The selective two-electron electrochemical oxygen reduction reaction (ORR) for hydrogen peroxide (H2O2) production is a promising and green alternative method to the current energy-intensive anthraquinone process used in industry. In this study, we develop a single-atom catalyst (CNT-D-O-Fe) by anchoring defect-stabilized and oxygen-coordinated iron atomic sites (Fe-O<sub>4</sub>) onto porous carbon nanotubes using a local etching strategy. Compared to O-doped CNTs with vacancy defects (CNT-D-O) and oxygen-coordinated Fe single-atom site modifying CNTs without a porous structure (CNT-O-Fe), CNT-D-O-Fe exhibits

- <sup>a</sup> College of Materials Science and Engineering, Sichuan University, Chengdu, 610065, P. R. China. E-mail: panpanli@scu.edu.cn
- <sup>b</sup> Institute for Advanced Study, Chengdu University, Chengdu, 610106, P. R. China <sup>c</sup> College of Chemical Engineering, Sichuan University, Chengdu, 610065,
- <sup>d</sup> Materials Science and Engineering Program and Walker Department of Mechanical Engineering, The University of Texas at Austin, Austin, Texas 78712, USA. E-mail: ghyu@austin.utexas.edu
- <sup>e</sup> Institute of Fundamental and Frontier Sciences, University of Electronic Science and Technology of China, Chengdu, 610054, P. R. China
- † Electronic supplementary information (ESI) available. See DOI: https://doi.org/ 10.1039/d3mh00882g



Guihua Yu

We would like to express our sincerest congratulations Materials Horizons remarkable 10-year anniversary. Our partnership with the journal dates back to our first publication in 2021 and has grown stronger ever since. It brings us great pride to be part of this prestigious journal's journey, as the journal has made impactful contributions to the field of materials science. Let us celebrate the continued success and productivity of

Materials Horizons for the next decade!

#### New concepts

The production of hydrogen peroxide (H2O2) through the electrocatalytic oxygen reduction reaction (ORR) requires catalytic materials with robust catalytic activity and high two-electron selectivity. The micro-environments of the catalytic sites play a crucial role in determining the catalytic performance. In this study, we present a novel approach to construct a unique oxygencoordinated iron single-atom site (Fe-O<sub>4</sub>) modified with vacancy defects on carbon nanotubes (CNT-D-O-Fe) using iron oxide-induced local etching. The oxygen-coordinated environment enhances the two-electron intrinsic reactivity for iron single-atom sites, while the vacancy defects greatly improve the electrocatalytic stability. As a result, CNT-D-O-Fe exhibits exceptional H2O2 selectivity, kinetic current density, and durable stability. Theoretical calculations further reveal that the oxygen-coordinated environment and the defective moiety of CNT-D-O-Fe efficiently optimize the adsorption strength of the \*OOH intermediate over the Fe single atomic active sites. This work provides an in-depth understanding of the effects of the microenvironmental structure on the reaction path and catalytic performance. The unique local coordinated environment regulation concept at the atomic scale paves a new way for the design of highly efficient transition-metal single-atom catalysts.

the highest H2O2 selectivity of 94.4% with a kinetic current density of 13.4 mA cm $^{-2}$ . Fe $-O_4$  single-atom sites in the catalyst probably contribute to the intrinsic reactivity for the two-electron transfer process while vacancy defects greatly enhance the electrocatalytic stability. Theoretical calculations further support that the coordinated environment and defective moiety in CNT-D-O-Fe could efficiently optimize the adsorption strength of the \*OOH intermediate over the Fe single atomic active sites. This contribution sheds light on the potential of defect-stabilized and oxygen-coordinated single-atom metal sites as a promising avenue for the rational design of highly efficient and selective catalysts towards various electrocatalytic reactions.

#### Introduction

With the rapid growth of the economy, the demand for hydrogen peroxide (H<sub>2</sub>O<sub>2</sub>) has been increasing significantly in various industries, such as bleaching, chemical synthesis, wastewater

Communication **Materials Horizons** 

treatment, and disinfection, with an expected need of 6 million tons by 2024.<sup>1-3</sup> However, the current industrial H<sub>2</sub>O<sub>2</sub> production primarily relies on the anthraquinone process, which is associated with inherent drawbacks, especially high energy consumption, which hinders green and sustainable development.<sup>4,5</sup> Therefore, it is crucial to explore eco-friendly and efficient alternative approaches for H<sub>2</sub>O<sub>2</sub> production. The electrocatalytic oxygen reduction reaction (ORR), powered by renewable energy, provides an attractive H<sub>2</sub>O<sub>2</sub> synthetic strategy through a twoelectron reaction pathway. However, the ORR involves complex O-O bond cleavage mechanisms, resulting in blend products of H<sub>2</sub>O<sub>2</sub> or H<sub>2</sub>O together with a slow kinetic rate. Thus, it is vital to design efficient catalysts to improve the selectivity and activity of H<sub>2</sub>O<sub>2</sub> electrosynthesis. The intrinsic performance is determined by the electronic structure of active sites, which influences the adsorption strength and activation state of reactants and intermediates during the electrocatalysis process. 7-13 In particular, the optimal binding energy between the reaction intermediate (\*OOH) and active sites can promote the preservation of the O-O bond to inhibit over-reduction and the formation of H<sub>2</sub>O.<sup>14-18</sup> Therefore, the rational modulation of the electronic structure enables efficient activity and high H2O2 selectivity of the active sites.19

Single-atom catalysts (SACs) offer remarkable advantages, including greatly increased atomic utilization and highly tunable electronic structures compared with bulk and nanocatalysts.<sup>20-26</sup> Specifically, the electronic structure of carbon-supported and nonmetallic heteroatom-coordinated metal-based SACs (such as a metal-nitrogen-carbon structure) can be tailor-tuned via a series of achievable strategies such as the adjustment of coordination environments, metal centers, and the density of the single atomic sites, with the aim of improving the catalytic performance. 4,6,12,23 Although some studies have confirmed that Fe-N-C SACs display efficient catalytic activity for the ORR, the catalytic reaction pathway mainly focuses on the four-electron reduction process producing H<sub>2</sub>O rather than H<sub>2</sub>O<sub>2</sub>. <sup>22,27–30</sup> Given this, the regulation of the micro-environment of Fe single-atom sites, such as nonmetallic coordination sites and the structure of the carbon substrate can be utilized to alter the reduction path and thus selectivity, while understanding the effects of the coordinated environment on the ORR activity of Fe single-atom sites is still lacking.

Herein, the oxygen-coordinated Fe single atomic site modifying multiwalled carbon nanotubes (CNTs) with abundant vacancy defects (CNT-D-O-Fe) is achieved by a local etching strategy, exhibiting the desired ORR catalytic performance. Meanwhile, the ORR catalytic activity, stability, and H2O2 selectivity of CNT-D-O-Fe greatly surpass those of O-doped CNTs with vacancy defects (CNT-D-O) and oxygen-coordinated Fe single-atom site modifying CNTs without porous structures (CNT-O-Fe). Density functional theory (DFT) calculations further reveal that synergistic effects between the oxygen-coordinated environment and vacancy defects substantially improve the adsorption strength of the \*OOH intermediate at the Fe single-atom active sites to enhance the two-electron ORR catalytic activity. This work provides an in-depth understanding of the effects of the coordination environment and vacancy defects on the reaction path and catalytic activity of the metal single-atom sites, which would benefit the precise design of single-atom catalysts with predictable performance.

#### Results and discussion

#### Materials synthesis and characterization

As shown in Fig. 1, the oxygen-coordinated iron single-atom sites (Fe-O<sub>4</sub>) are anchored on the vacancy defect-rich CNTs (CNT-D-O-Fe) via a distinctive iron oxide-induced local etching strategy. Before the etching treatment, the pore-forming reagents (ironbased compounds) are evenly loaded on the CNTs with a smooth surface (Fig. 2a) to obtain the CNT-Fe-OH (Fig. S1, ESI†). After high-temperature etching, the generated sample displays abundant porous structures (Fig. S2, ESI†) and iron-based compounds transform into Fe<sub>2</sub>O<sub>3</sub> nanoparticles according to the XRD pattern in Fig. S3 (ESI†). Then CNT-D-O-Fe is obtained via further acid treatment to thoroughly remove the residual Fe<sub>2</sub>O<sub>3</sub>. The thermal gravity (TG) and differential thermal gravity (DTG) curves in Fig. S4 (ESI†) show that the carbon species in CNT-Fe-OH start to break down at ca. 470 °C and the weight decreases rapidly at ca. 565 °C. The corresponding temperatures of the original CNT (ca. 510 °C and ca. 603 °C, respectively) are significantly higher than CNT-Fe-OH. Therefore, the local carbon species in CNT-Fe-OH lose high thermal stability due to the induction of iron-based compounds, which facilitates the formation of defect structures in the obtained CNT-D-O-Fe.

Differing from the CNT with a smooth surface (Fig. 2a), CNT-D-O-Fe based on the optimal preparation conditions demonstrates abundant defective structures over the CNT (Fig. 2b and Fig. S5, ESI†). The transmission electron microscope (TEM) image (Fig. 2c) of CNT-D-O-Fe further confirms the presence of pores. Furthermore, the high-resolution transmission electron microscope (HRTEM) image and the local fast Fourier transform (FFT) patterns near the porous structures (Fig. 2d and the inset) show the breakage and the increase in disorder regarding the lattice fringes of CNTs. This result suggests that the formation of porous structures also induces a reduced degree of graphitization for carbon. The high-angle annular dark fieldscanning transmission electron microscopy (HAADF-STEM) image of CNT-D-O-Fe in Fig. 2e exhibits a vacancy defect around the porous structure. The isolated bright spots with a diameter of ca. 0.1 nm in the defect structure can be assigned to

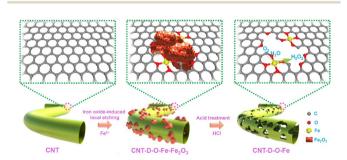


Fig. 1 Schematic of the preparation process of CNT-D-O-Fe.

**Materials Horizons** Communication

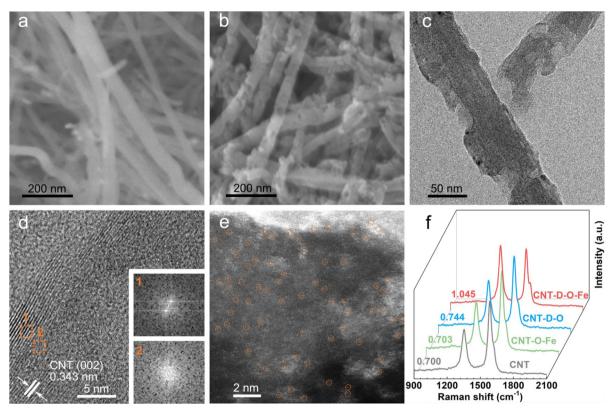


Fig. 2 (a) SEM image of CNTs; (b) SEM and (c) TEM images of CNT-D-O-Fe; (d) HRTEM image of CNT-D-O-Fe and the corresponding fast Fourier transform (FFT) patterns (the inset) of the local CNT-D-O-Fe around the vacancy defects; (e) HAADF-STEM image of CNT-D-O-Fe; (f) Raman spectra of the samples.

the isolated iron single atoms, revealing the successful introduction of iron single-atom sites during the etching process.

The control sample, CNT-O-Fe (0.03 wt% for iron content, Table S1, ESI†) only containing iron sites and without pore structure, is prepared via heating CNT-Fe-OH in an argon environment and the subsequent acid treatment. Similar to the CNT, the CNT-O-Fe shows a smooth surface (Fig. S6, ESI†), but iron sites are uniformly introduced in the CNT-O-Fe based on the element mapping of Fe in Fig. S7 (ESI†). In contrast, a limited number of porous structures are observed over CNT-D-O after a similar treatment of CNT-D-O-Fe except for the addition of Fe compounds (Fig. S8 and S9, ESI†). This result demonstrates the pivotal role of iron-based compounds in making defective porous structures of CNT.

Pore diameter distribution and (Brunauer-Emmett-Teller) BET-specific surface area of CNT, CNT-O-Fe, CNT-D-O, and CNT-D-O-Fe are analyzed based on the nitrogen adsorptiondesorption curves (Fig. S10a, ESI†). The presence of lots of porous structures makes CNT-D-O-Fe show a higher BETspecific surface area (Table S2, 195.2 m<sup>2</sup> g<sup>-1</sup>, ESI†), superior to CNT-O-Fe (82.1 m<sup>2</sup> g<sup>-1</sup>), CNT-D-O (116.9 m<sup>2</sup> g<sup>-1</sup>), and CNT  $(81.7 \text{ m}^2 \text{ g}^{-1})$ . Fig. S10b (ESI†) also displays the larger pore size distributions of CNT-D-O-Fe compared with CNT-D-O, CNT-O-Fe, and CNT. The higher specific surface area and bigger pore structure suggest a better mass transfer for CNT-D-O-Fe during electrocatalysis. To investigate the degree of graphitization of

carbon in these samples, the Raman tests are conducted and shown in Fig. 2f. The ratio of the peak intensities of D and G peaks (1342 cm<sup>-1</sup> and 1570 cm<sup>-1</sup>, respectively) for CNT-D-O-Fe is 1.045, higher than those of CNT-D-O (0.744), CNT-O-Fe (0.703) and CNT (0.700). This result demonstrates that the abundant porous structures make CNT-D-O-Fe have a lower degree of graphitization of carbon with more vacancy defects.<sup>31–33</sup> These characteristics are beneficial to the exposure of the active sites and the improvement of adsorption strength for the reactants.<sup>34–36</sup>

The X-ray photoelectron spectroscopy (XPS) survey spectrum of CNT-D-O-Fe in Fig. S11a (ESI†) reveals the presence of Fe, O, and C. The O 1s XPS peaks at ca. 531.7 eV (Fig. S11c, ESI†) can be assigned to the oxygen species in C-O-Fe. 37-40 However, the low Fe content in CNT-D-O-Fe (0.15 wt%, Table S1, ESI†) makes it difficult to confirm the chemical valence state and the corresponding fine structure of the iron single atoms only based on the XPS analysis. Therefore, the XAFS spectroscopy is further used to precisely explore the fine structure of CNT-D-O-Fe including the coordination environment and chemical state of the iron site. According to the Fe K-edge X-ray absorption near edge structure (XANES) of CNT-D-O-Fe, Fe<sub>2</sub>O<sub>3</sub>, and Fe foil in Fig. 3a, the oxidation state of iron in CNT-D-O-Fe is about +3 based on the similar rising-edge position (ca. 7120.6 eV) and the pre-edge peak (ca. 7115.6 eV) for CNT-D-O-Fe compared with Fe<sub>2</sub>O<sub>3</sub>. However, the unique planar geometry of the oxygen-coordinated single atomic iron sites (Fe-O<sub>4</sub>) makes CNT-D-O-Fe show a different

Communication

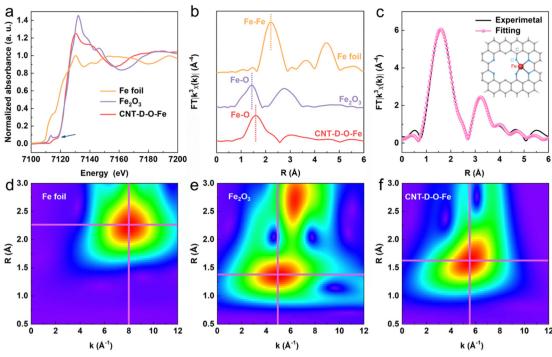


Fig. 3 (a) XANES and (b) FT-EXAFS of Fe foil, Fe<sub>2</sub>O<sub>3</sub>, and CNT-D-O-Fe, the intensity of Fe foil is halved. (c) The fitting curves of Fe K-edge EXAFS spectra of the CNT-D-O-Fe in R space and the optimized Fe-O<sub>4</sub> structure with defects (the inset, gray ball: C atom, blue ball: O atom, red ball: Fe atom). WT plots of (d) Fe foil, (e) Fe<sub>2</sub>O<sub>3</sub>, and (f) CNT-D-O-Fe based on the EXAFS.

first derivative of the Fe K-edge XANES signal in comparison to  $Fe_2O_3$  (Fig. S13, ESI†).<sup>37</sup> Besides, the peak at ca.1.52 Å in the Fourier transform of the Fe K-edge extended X-ray absorption fine structure (FT-EXAFS) (Fig. 3b) reveals that the iron atom in CNT-D-O-Fe is mainly bonded to O atoms instead of other Fe atoms (ca. 2.20 Å for Fe-Fe bond). The Fe-O bond length in CNT-D-O-Fe (ca. 1.52 Å) differs from that in Fe<sub>2</sub>O<sub>3</sub> (ca. 1.46 Å). Additionally,  $Fe_2O_3$  exhibits an observable peak at ca. 2.76 Å, attributed to the Fe-Fe interaction in the second coordination shell, while such a signal is absent in CNT-D-O-Fe due to its unique single-atom coordination environment. According to the above analysis, the vacancy defect modifying oxygencoordinated iron single atomic site (Fe-O<sub>4</sub>) is used as the model structure (the inset of Fig. 3c) to fit the FT-EXAFS spectrum. The fitting results in k and R spaces are well matched with the experimental results (Fig. 3c and Fig. S14, ESI†). The fitting model structure based on the experimental data shows the Fe-O coordination number of ca. 3.60 with a bonding length of ca. 2.06 Å (Table S3, ESI†). Besides, the wavelet transform (WT) plots (Fig. 3d-f) of Fe foil, Fe<sub>2</sub>O<sub>3</sub>, and CNT-D-O-Fe are performed according to the values of *k* and *R* spaces to better visualize the corresponding EXAFS spectra. With regard to the CNT-D-O-Fe, only one main peak at 1.3-2.0 Å and 4-7 Å<sup>-1</sup> is assigned to the Fe-O bond, which is obviously different from the Fe-O bond  $(1.2-1.6 \text{ Å} \text{ and } 3-7 \text{ Å}^{-1})$  in Fe<sub>2</sub>O<sub>3</sub>. Besides, another strong peak for  $Fe_2O_3$  can be attributable to the Fe-Fe shell in oxides.<sup>41,42</sup> The above results involving the composition and fine structure fully demonstrate that the in situ partial etching functionalization strategy induced by iron oxide successfully prepares the

oxygen-coordinated single-atom iron site on defects-rich CNT (CNT-D-O-Fe).

#### Electrocatalytic 2e -- ORR performance

The ORR catalytic performances toward H<sub>2</sub>O<sub>2</sub> production for CNT-D-O-Fe and the as-prepared control materials (CNT-D-O, CNT-O-Fe, and CNT) are evaluated in the O2-saturated 0.1 M KOH solution (Fig. S15, ESI†) via the rotating ring disk electrode (RRDE). The linear sweep voltammograms (LSV) recorded at a rotation speed of 1600 rpm are shown in Fig. 4a. The pristine CNT only displays an unfavorable cathodic current density (-2.20 mA cm<sup>-2</sup> at 0.550 V vs. reversible hydrogen electrode (RHE)) and the low onset potential of 0.771 V vs. RHE (determined at the current density of 0.150 mA cm<sup>-2</sup>) among the group of curves.<sup>4</sup> After introducing abundant vacancy defects and oxygen-coordinated single-atom iron sites, the ORR reduction current density of CNT-D-O-Fe greatly increases  $(-2.72 \text{ mA cm}^{-2} \text{ at } 0.550 \text{ V})$  vs. RHE) with the high onset potential of 0.823 V vs. RHE. However, the catalysts with the modification of iron sites (CNT-O-Fe, -2.36mA cm<sup>-2</sup> at 0.550V vs. RHE, 0.776 V vs. RHE) or oxygen-induced vacancy defects (CNT-D-O, -2.48 mA cm<sup>-2</sup> at 0.550 V vs. RHE, 0.803 V vs. RHE) both show inferior reduction current density and lower onset potential compared with the CNT-D-O-Fe. The Tafel plots in Fig. 4b exhibit similar slopes (approximately 80 mV dec<sup>-1</sup>) for the samples in this study, suggesting an identical reaction mechanism with the first electron transfer to O2 being the ratedetermining step under Temkin adsorption isotherm conditions.<sup>43</sup> Additionally, the kinetic current density of CNT-D-O-Fe at 0.550 V vs. RHE is 13.4 mA cm<sup>-2</sup> (Fig. 4c). This value is higher than those

Materials Horizons Communication

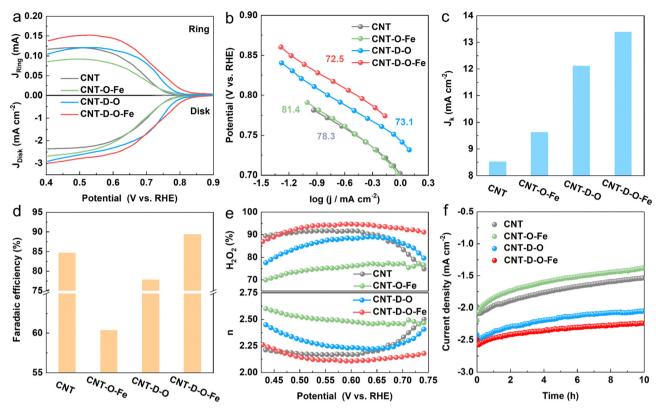


Fig. 4 (a) LSV curves (ring current and disk current density, respectively), (b) the Tafel plots of CNT, CNT-O-Fe, CNT-D-O, and CNT-D-O-Fe; (c)  $J_k$  and (d) faradaic efficiency for  $H_2O_2$  at 0.550 V vs. RHE, (e) electron transfer number and selectivity for  $H_2O_2$ ; (f) stability test of the catalytic materials at 0.550 V vs. RHE.

of other catalysts, including CNT-D-O (12.1 mA cm<sup>-2</sup>), CNT-O-Fe (9.62 mA cm<sup>-2</sup>), and CNT (8.52 mA cm<sup>-2</sup>), further highlighting the superior intrinsic catalytic performance of CNT-D-O-Fe. The results imply that the defective structure and oxygen-coordinated Fe single-atom sites could efficiently contribute to the ORR kinetic rate.

The faradaic efficiency, selectivity of  $\rm H_2O_2$ , and the electron transfer number were calculated based on the corresponding ring and disk current. As shown in Fig. 4 and Fig. S16 (ESI†), CNT-D-O-Fe displays high faradaic efficiency (89.4%) and selectivity for  $\rm H_2O_2$  (94.4%) at 0.550 V  $\nu s$ . RHE, which is better than CNT-D-O, CNT-O-Fe, CNT and some previously reported catalysts (Table S4, ESI†). Furthermore, compared with CNT-D-O, CNT-O-Fe, and CNT, CNT-D-O-Fe is more likely to undergo ORR  $\nu ia$  the two-electron transfer pathway as shown in Fig. 4e.

In addition, although CNT-O-Fe and CNT-D-O display higher ORR reduction current densities, their  $\rm H_2O_2$  selectivity (75.3% and 87.5%, respectively) is lower than that of the CNT (91.7%). This difference suggests that the individual introduction of vacancy defects or iron single-atom sites would not enhance the  $\rm H_2O_2$  production efficiency. Nevertheless, the synergistic combination of oxygen-coordinated iron single-atom sites (Fe-O<sub>4</sub>) and vacancy defects in CNT-D-O-Fe greatly increases the ORR activity (higher reduction current density) while promoting the two-electron pathway to improve the  $\rm H_2O_2$  selectivity. Chronoamperometry (at 0.550 V  $\nu s$ . RHE for 600 min) was conducted to evaluate the catalytic stability. The current density of CNT-D-O-Fe shows little noticeable fluctuation and can retain about 90.2% of

the initial current density after the electrolysis for 10 h. But the current densities of CNT-O-Fe and CNT-D-O are only 84.7% and 63.0% of the initial value, which reveals that the existence of defects remarkably enhances the catalytic stability of iron single-atom sites in CNT-D-O-Fe. It is postulated that the introduction of the vacancy defect could increase the unsaturation of the carbon substrate, thereby enhancing the interaction between single atomic sites and the substrate. This effectively mitigated the dissolution and aggregation of metal atoms during the catalytic process. 44,45 So the CNT-D-O-Fe shows high catalytic stability.

# Theoretical insights into the electrocatalyst for the ORR mechanism

To investigate the mechanism of the advanced two-electron ORR catalytic performance of CNT-D-O-Fe in depth, the optimized model structures (Fig. 5a) including CNT-D-O-Fe, CNT-O-Fe, CNT-D-O, CNT-O, and CNT-D were constructed to perform the density functional theory (DFT) calculations. Furthermore, Fig. 5b and Fig. S17 (ESI $^\dagger$ ) provide the side and top views of the optimal theoretical models (CNT-D-O-Fe and CNT-O-Fe) with and without adsorption of O $_2$  and \*OOH species, respectively.

Clearly, the introduction of vacancy defects alters the configuration of the iron single atomic site and subsequently affects the adsorption state of both  $O_2$  and \*OOH species. This fundamental alteration serves as the underlying reason for the observed disparity in the catalytic activity. In principle, the two-electron ORR first undergoes one-electron reduction (from  $O_2$ 

Communication **Materials Horizons** 

to \*OOH), and then \*OOH is further reduced to H<sub>2</sub>O<sub>2</sub>. Since both processes involve \*OOH intermediates, the free energy of adsorbed \*OOH species ( $\Delta G$ (\*OOH)) serves as a critical descriptor for evaluating the catalytic activity of the two-electron ORR that produces  ${\rm H_2O_2.}^{46-49}$  To this end,  $\Delta G({\rm ^*OOH})$  of all model structures at the equilibrium potential (0.700 V vs. RHE) was calculated and is shown in Fig. 5c. Obviously, the  $\Delta G(*OOH)$  of CNT-D-O-Fe (3.46 eV) is very close to the ideal value (3.52 eV) and indicates a moderate adsorption strength for \*OOH. In contrast, the adsorption strength of \*OOH on CNT-O (3.92 eV) and CNT-O-Fe (3.77 eV) is too weak, while it is too strong for CNT-D-O (3.40 eV) and CNT-D (3.22 eV). The limiting potential  $(U_{\rm L})$  is defined as the maximum potential at which both two

one-electron reduction steps (from O<sub>2</sub> to \*OOH and subsequent reduction from \*OOH to H2O2) become thermodynamically favorable.<sup>50</sup> Therefore, the activity volcano plots based on the  $U_{\rm L}$  and  $\Delta G(*OOH)$  are summarized to further underline the intrinsic activity of the catalyst models (Fig. 5d). The most efficient activity with zero overpotential is the vertex value of the volcano at the equilibrium potential (0.700 V vs. RHE). 47,50,51 Notably, the CNT-D-O-Fe exhibits the highest catalytic activity for the two-electron reduction of O2 to H2O2 with an overpotential of merely 0.06 V. This value is essentially lower than those of other theoretical models, including CNT-O-Fe (0.25 V), CNT-D-O (0.12 V), CNT-O (0.40 V), and CNT-D (0.30 V). The computational results suggest that the synergy between vacancy

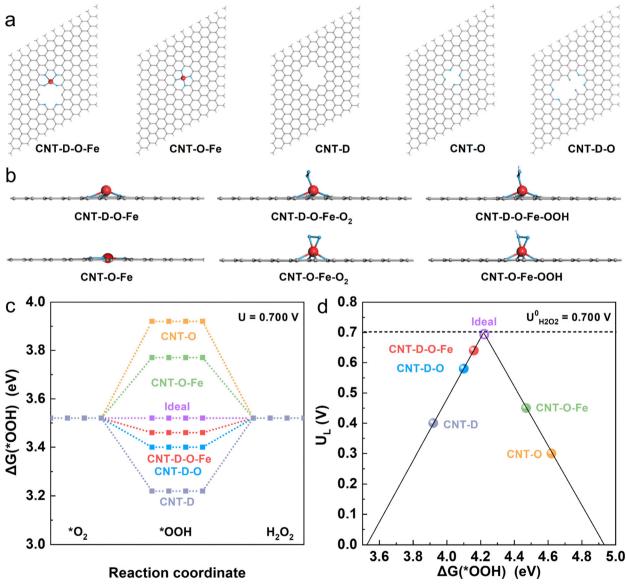


Fig. 5 (a) The optimized structures for CNT-D-O-Fe, CNT-O-Fe, CNT-O, and CNT-D-O; (b) the side view of the optimal theoretical models (CNT-D-O-Fe, CNT-O-Fe) with and without adsorption of O2 and \*OOH species (gray ball: C atom, blue ball: O atom, red ball: Fe atom, white ball: H atom). (c) Free-energy diagram for  $O_2$ -to- $H_2O_2$  on these optimal model structures at the equilibrium potential (U = 0.700 V). (d) Catalytic activity volcano plot with the calculated limiting potential  $(U_L)$  as the y-axis and the calculated free energy of \*OOH as the x-axis. The standard redox potential of the twoelectron ORR (0.700 V) is displayed via the horizontal dashed line.

defect and oxygen-coordinated environment effectively improves the adsorption strength of \*OOH intermediates on single atomic iron sites, resulting in robust ORR catalytic activity and high  $\rm H_2O_2$  selectivity (Fig. 4).

#### Conclusions

**Materials Horizons** 

In summary, we have successfully designed and synthesized CNT-D-O-Fe, featuring oxygen-coordinated iron single-atom sites (Fe-O<sub>4</sub>) modified with vacancy defects. CNT-D-O-Fe exhibits highly efficient ORR catalytic activity and remarkable H2O2 selectivity when compared to other catalysts such as CNT, CNT-D-O, and CNT-O-Fe, with the presence of vacancy defects contributing to its robust catalytic stability. Theoretical calculations further confirm the enhancement of  $\Delta G(*OOH)$  for CNT-D-O-Fe, resulting from the synergistic effect between vacancy defects and oxygen-coordinated environments. Our work provides a revealing example of defectstabilized and oxygen-coordinated metal single-atom materials as advanced catalysts for the ORR to produce H<sub>2</sub>O<sub>2</sub>. Furthermore, it offers a deeper insight into the roles of coordination environments and defects on catalytic performance, and also opens up new possibilities for designing unique single-atom catalysts with high activity and selectivity. We believe that our findings could contribute significantly to the development of versatile and low-cost electrocatalysts for more important reactions beyond oxygen reduction to hydrogen peroxide.

#### Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

P.L. acknowledges the funding support from the National Nature Science Foundation of China (No. 52202372), the Sichuan Science and Technology Program (2023NSFSC0436 and 2023NSFSC0089), and the Fundamental Research Funds for the Central Universities (YJ2021151). G.Y. acknowledges the funding support from the Welch Foundation Award F-1861, the Norman Hackerman Award in Chemical Research by the Welch Foundation, and the Camille Dreyfus Teacher-Scholar Award. T.G. acknowledges the Chengdu University new faculty start-up funding (No. 2081920074). The authors would like to thank Xie Han from Shiyanjia Lab (www.shiyanjia.com) for the XPS tests.

#### Notes and references

- 1 H. W. Kim, M. B. Ross, N. Kornienko, L. Zhang, J. Guo, P. Yang and B. D. McCloskey, *Nat. Catal.*, 2018, **1**, 282–290.
- 2 S. J. Freakley, Q. He, J. H. Harrhy, L. Lu, D. A. Crole, D. J. Morgan, E. N. Ntainjua, J. K. Edwards, A. F. Carley, A. Y. Borisevich, C. J. Kiely and G. J. Hutchings, *Science*, 2016, 351, 965–968.
- 3 S. Yang, A. Verdaguer-Casadevall, L. Arnarson, L. Silvioli, V. Čolić, R. Frydendal, J. Rossmeisl, I. Chorkendorff and I. E. L. Stephens, *ACS Catal.*, 2018, **8**, 4064–4081.

- 4 H. Gong, Z. Wei, Z. Gong, J. Liu, G. Ye, M. Yan, J. Dong, C. Allen, J. Liu, K. Huang, R. Liu, G. He, S. Zhao and H. Fei, *Adv. Funct. Mater.*, 2022, 32, 2106886.
- 5 K. H. Koh, A. H. Bagherzadeh Mostaghimi, Q. Chang, Y. J. Kim, S. Siahrostami, T. H. Han and Z. Chen, *EcoMat*, 2022, 5, e12266.
- 6 Y. Wu, Y. Ding, X. Han, B. Li, Y. Wang, S. Dong, Q. Li, S. Dou, J. Sun and J. Sun, Appl. Catal., B, 2022, 315, 121578.
- 7 Z. Deng and X. Wang, Nano Res., 2022, 15, 4599-4605.
- 8 P. Wang, Z. Jin, P. Li and G. Yu, Chem. Catal., 2022, 2, 1277-1287.
- 9 T. Gao, C. Zhou, X. Chen, Z. Huang, H. Yuan and D. Xiao, J. Mater. Chem. A, 2020, 8, 18367–18375.
- 10 W. Qiu, X. Chen, Y. Liu, D. Xiao, P. Wang, R. Li, K. Liu, Z. Jin and P. Li, *Appl. Catal.*, *B*, 2022, 315, 121548.
- 11 W. Qiu, M. Xie, P. Wang, T. Gao, R. Li, D. Xiao, Z. Jin and P. Li, *Small*, 2023, 2300437.
- 12 Z. Jin, Anal. Chem., 2023, 95, 6477-6489.
- 13 T. Gao, S. Yu, Y. Chen, X. Li, X. Tang, S. Wu, B. He, H. Lan, S. Li, Q. Yue and D. Xiao, *J. Colloid Interface Sci.*, 2023, 642, 120–128.
- 14 Q. Yang, W. Xu, S. Gong, G. Zheng, Z. Tian, Y. Wen, L. Peng, L. Zhang, Z. Lu and L. Chen, *Nat. Commun.*, 2020, **11**, 5478.
- 15 E. Jung, H. Shin, W. Hooch Antink, Y. E. Sung and T. Hyeon, *ACS Energy Lett.*, 2020, 5, 1881–1892.
- 16 Z. Wang, Q. K. Li, C. Zhang, Z. Cheng, W. Chen, E. A. McHugh, R. A. Carter, B. I. Yakobson and J. M. Tour, ACS Catal., 2021, 11, 2454–2459.
- 17 M. Melchionna, P. Fornasiero and M. Prato, *Adv. Mater.*, 2019, 31, 1802920.
- 18 Y. Jia, Z. Xue, J. Yang, Q. Liu, J. Xian, Y. Zhong, Y. Sun, X. Zhang, Q. Liu, D. Yao and G. Li, *Angew. Chem., Int. Ed.*, 2022, **61**, e202110838.
- 19 J. H. Kim, Y. T. Kim and S. H. Joo, *Curr. Opin. Electrochem.*, 2020, **21**, 109–116.
- 20 P. Li, Z. Fang, Z. Jin and G. Yu, Chem. Phys. Rev., 2021, 2, 041305.
- 21 Z. Jin, P. Li, Z. Fang and G. Yu, Acc. Chem. Res., 2022, 55, 759-769.
- 22 T. Gao, X. Tang, X. Li, S. Wu, S. Yu, P. Li, D. Xiao and Z. Jin, *ACS Catal.*, 2022, **13**, 49–59.
- 23 Z. Jin, P. Li, Y. Meng, Z. Fang, D. Xiao and G. Yu, *Nat. Catal.*, 2021, **4**, 615–622.
- 24 Z. Jin and A. J. Bard, *Proc. Natl. Acad. Sci. U. S. A.*, 2020, 117, 12651.
- 25 P. Li, R. Li, Y. Liu, M. Xie, Z. Jin and G. Yu, *J. Am. Chem. Soc.*, 2023, **145**, 6471–6479.
- 26 P. Li, L. Liao, Z. Fang, G. Su, Z. Jin and G. Yu, *Proc. Natl. Acad. Sci. U. S. A.*, 2023, 120, e2305489120.
- 27 M. Xiao, J. Zhu, L. Ma, Z. Jin, J. Ge, X. Deng, Y. Hou, Q. He, J. Li, Q. Jia, S. Mukerjee, R. Yang, Z. Jiang, D. Su, C. Liu and W. Xing, ACS Catal., 2018, 8, 2824–2832.
- 28 Y. Yan, H. Cheng, Z. Qu, R. Yu, F. Liu, Q. Ma, S. Zhao, H. Hu, Y. Cheng, C. Yang, Z. Li, X. Wang, S. Hao, Y. Chen and M. Liu, *J. Mater. Chem. A*, 2021, 9, 19489–19507.
- 29 C. Zhu, Q. Shi, B. Z. Xu, S. Fu, G. Wan, C. Yang, S. Yao, J. Song, H. Zhou, D. Du, S. P. Beckman, D. Su and Y. Lin, *Adv. Energy Mater.*, 2018, 8, 1801956.

Communication **Materials Horizons** 

- 30 H. Yang, Z. Li, S. Kou, G. Lu and Z. Liu, Appl. Catal., B, 2020, 278, 119270.
- 31 D. Pan, S. Wang, B. Zhao, M. Wu, H. Zhang, Y. Wang and Z. Jiao, Chem. Mater., 2009, 21, 3136-3142.
- 32 M. A. Pimenta, G. Dresselhaus, M. S. Dresselhaus, L. G. Cancado, A. Jorio and R. Saito, Phys. Chem. Chem. Phys., 2007, 9, 1276-1290.
- 33 T. Gao, C. Zhou, Y. Zhang, Z. Jin, H. Yuan and D. Xiao, J. Mater. Chem. A, 2018, 6, 21577-21584.
- 34 T. Gao, X. Li, X. Chen, C. Zhou, Q. Yue, H. Yuan and D. Xiao, Chem. Eng. J., 2021, 424, 130416.
- 35 T. Gao, S. Wu, X. Li, C. Lin, Q. Yue, X. Tang, S. Yu and D. Xiao, Inorg. Chem. Front., 2022, 9, 3598-3608.
- 36 R. Li, T. Gao, P. Wang, W. Qiu, K. Liu, Y. Liu, Z. Jin and P. Li, Appl. Catal., B, 2023, 331, 122677.
- 37 S. Zhang, M. Jin, T. Shi, M. Han, Q. Sun, Y. Lin, Z. Ding, L. R. Zheng, G. Wang, Y. Zhang, H. Zhang and H. Zhao, Angew. Chem., Int. Ed., 2020, 59, 13423-13429.
- 38 X. Li, Y. Guo, T. Gao, P. Li, Z. Jin and D. Xiao, ACS Appl. Mater. Interfaces, 2021, 13, 57411-57421.
- 39 Z. Mou, J. Peng, R. Yan, Q. Yang, B. Zhao and D. Xiao, Carbon, 2023, 203, 11-20.
- 40 Z. Mou, R. Yan, J. Peng, Y. Li, Z. Huang, Z. Wang, B. Zhao and D. Xiao, Chem. Eng. J., 2023, 465, 142986.
- 41 P. Li, Z. Jin, Z. Fang and G. Yu, Energy Environ. Sci., 2021, 14, 3522-3531.

- 42 J. M. Vega and H. Kamin, J. Biol. Chem., 1977, 252, 896-909.
- 43 N. Ramaswamy and S. Mukerjee, J. Phys. Chem. C, 2011, 115, 18015-18026.
- 44 Y. Zhang, L. Guo, L. Tao, Y. Lu and S. Wang, Small Methods, 2019, 3, 1800406.
- 45 P. Zhu, P. Song, W. Feng, D. Zhao, T. Liu, J. Zhang and C. Chen, J. Mater. Chem. A, 2020, 10, 17948.
- 46 S. Siahrostami, A. Verdaguer-Casadevall, M. Karamad, D. Deiana, P. Malacrida, B. Wickman, M. Escudero-Escribano, E. A. Paoli, R. Frydendal, T. W. Hansen, I. Chorkendorff, I. E. L. Stephens and J. Rossmeisl, Nat. Mater., 2013, 12, 1137-1143.
- 47 H. Li, P. Wen, D. S. Itanze, Z. D. Hood, S. Adhikari, C. Lu, X. Ma, C. Dun, L. Jiang, D. L. Carroll, Y. Qiu and S. M. Geyer, Nat. Commun., 2020, 11, 3928.
- Verdaguer-Casadevall, D. Deiana, M. Karamad, 48 A. S. Siahrostami, P. Malacrida, T. W. Hansen, J. Rossmeisl, I. Chorkendorff and I. E. L. Stephens, Nano Lett., 2014, 14, 1603-1608.
- 49 A. Kulkarni, S. Siahrostami, A. Patel and J. K. Nørskov, Chem. Rev., 2018, 118, 2302-2312.
- 50 Z. Lu, G. Chen, S. Siahrostami, Z. Chen, K. Liu, J. Xie, L. Liao, T. Wu, D. Lin, Y. Liu, T. F. Jaramillo, J. K. Nørskov and Y. Cui, Nat. Catal., 2018, 1, 156-162.
- 51 Q. Chang, P. Zhang, A. H. B. Mostaghimi, X. Zhao, S. R. Denny, J. H. Lee, H. Gao, Y. Zhang, H. L. Xin, S. Siahrostami, J. G. Chen and Z. Chen, Nat. Commun., 2020, 11, 2178.