

Cite this: *Nanoscale*, 2016, 8, 6317

# Experimental and theoretical optical properties of methylammonium lead halide perovskites†

Aurélien M. A. Leguy,<sup>‡a</sup> Pooya Azarhoosh,<sup>‡b</sup> M. Isabel Alonso,<sup>c</sup>  
Mariano Campoy-Quiles,<sup>c</sup> Oliver J. Weber,<sup>d</sup> Jizhong Yao,<sup>a</sup> Daniel Bryant,<sup>e,f</sup>  
Mark T. Weller,<sup>d</sup> Jenny Nelson,<sup>a,f</sup> Aron Walsh,<sup>d</sup> Mark van Schilfgaarde<sup>\*b</sup> and  
Piers R. F. Barnes<sup>\*a</sup>

The optical constants of methylammonium lead halide single crystals  $\text{CH}_3\text{NH}_3\text{PbX}_3$  ( $\text{X} = \text{I}, \text{Br}, \text{Cl}$ ) are interpreted with high level *ab initio* calculations using the relativistic quasiparticle self-consistent GW approximation (QSGW). Good agreement between the optical constants derived from QSGW and those obtained from spectroscopic ellipsometry enables the assignment of the spectral features to their respective inter-band transitions. We show that the transition from the highest valence band (VB) to the lowest conduction band (CB) is responsible for almost all the optical response of  $\text{MAPbI}_3$  between 1.2 and 5.5 eV (with minor contributions from the second highest VB and the second lowest CB). The calculations indicate that the orientation of  $[\text{CH}_3\text{NH}_3]^+$  cations has a significant influence on the position of the bandgap suggesting that collective orientation of the organic moieties could result in significant local variations of the optical properties. The optical constants and energy band diagram of  $\text{CH}_3\text{NH}_3\text{PbI}_3$  are then used to simulate the contributions from different optical transitions to a typical transient absorption spectrum (TAS).

Received 11th August 2015,  
Accepted 30th September 2015

DOI: 10.1039/c5nr05435d

www.rsc.org/nanoscale

## Introduction

Hybrid organic–inorganic methylammonium lead halide perovskite semiconductors  $\text{MAPbX}_3$  ( $\text{MA} = \text{CH}_3\text{NH}_3$ ;  $\text{X} = \text{I}, \text{Br}, \text{Cl}$ ) are at the centre of a tremendous research effort in the field of photovoltaics. The outstanding optical properties of  $\text{MAPbI}_3$  have been fundamental to the success of hybrid perovskites as active material for solar cells.

$\text{MAPbI}_3$  has a bandgap – believed to be direct – located between 1.5 and 1.6 eV, reasonably close to the optimum given by Shockley-Queisser theory<sup>1</sup> (the maximum single band gap efficiency is ~33.7% at 1.4 eV compared to  $\text{MAPbI}_3$  at ~30% to 32%). This, combined with its high absorption coefficient – about 280 nm of  $\text{MAPbI}_3$  is enough to absorb ~80% of the

incident sun light below the bandgap<sup>2</sup> – make the material an excellent candidate for highly efficient thin film single junction solar cells. Developing a deeper understanding of the optical properties is important both practically and more fundamentally. For example, detailed knowledge of the optical constants enables both harvesting and out coupling of light within layers to be optimised in solar cells, lasers and LEDs.<sup>3</sup> Another example relates to the use of transient absorption spectroscopy (TAS) which is widely used as a means to probe charge carrier dynamics in materials. The optical features observed in TAS for  $\text{MAPbX}_3$  have not yet been confidently assigned making it difficult to know what the measurements are really telling us.

The theoretical optoelectronic properties of  $\text{MAPbX}_3$  are still under debate. Band diagrams vary widely, depending on the level of approximation employed; Fig. 1 compares various calculations of the fundamental band gap. In addition to the fundamental gaps, the band dispersions (band energy vs. crystal momentum) are also sensitive to the different levels of approximation. This sensitivity is greater than for conventional tetrahedral semiconductors because of the very heterogeneous composition of the hybrid perovskites. Density functional theory (DFT) tends to underestimate the binding of occupied states, as well as the splitting between occupied and unoccupied ones. The error in the quasiparticle level depends on the element; thus there is typically significant misalignment of

<sup>a</sup>Physics department, Imperial College London, SW7 2AZ, UK.

E-mail: piers.barnes@imperial.ac.uk

<sup>b</sup>Physics department, Kings College London, WC2R 2LS, UK.


E-mail: mark.van\_schilfgaarde@kcl.ac.uk

<sup>c</sup>Institut de Ciència de Materials de Barcelona (ICMAB-CSIC), 08193, Spain<sup>d</sup>Chemistry department, University of Bath, BA2 7AY, UK<sup>e</sup>Chemistry department, Imperial College, London, SW7 2AZ, UK<sup>f</sup>SPECIFIC, College of Engineering, Swansea University, Baglan Bay Innovation and Knowledge Centre, Central Avenue, Baglan, SA12 7AX, UK

†Electronic supplementary information (ESI) available. See DOI: 10.1039/c5nr05435d

‡Both authors equally contributed to the work.



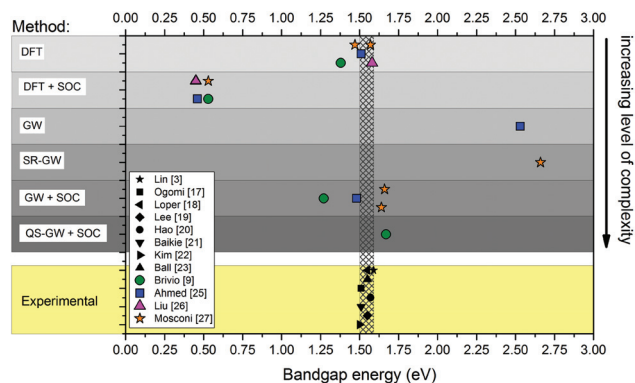

**Fig. 1** Comparison of the reported experimental bandgaps of MAPbI<sub>3</sub> (obtained by absorption spectroscopy,<sup>17–19</sup> diffuse reflectance spectroscopy,<sup>20–22</sup> device stack ellipsometry<sup>23</sup>) from both experimental studies<sup>3,17–24</sup> and first principles calculations.<sup>9,25–27</sup> The hatched area that encompasses the black markers corresponds to the spread of experimental values (~0.1 eV). The coloured markers show the position of calculated bandgaps from various *ab initio* studies (the type of method is specified on the left). SRGW stands for scalar relativistic GW.<sup>27</sup>

levels in heterogeneous materials. Semi-empirical corrections, *e.g.* hybrid functionals, are tailored to improve only the bandgap, but their effect on individual levels is less clear. Thus, even if different computational methods yield similar bandgaps, not all of them give meaningful information about the electronic band structure.

The *ab initio* methods used to calculate the energy band diagram of MAPbI<sub>3</sub> generally divide into density-based and Green's function based schemes (Fig. 1). Inexpensive density-based implementations such as local-density approximation (LDA),<sup>4,5</sup> semi-local generalized gradient approximations (GGA)<sup>6</sup> and PBE (Perdew–Burke–Ernzerhof functional)<sup>7</sup> give a fortuitously good fundamental gap by neglecting spin-orbit coupling (SOC). However, it was realized that this good agreement results from a cancellation of errors,<sup>8,9</sup> spin-orbit interactions (SOC) are in fact of foremost importance to the optoelectronic properties of the material – they account for up to 1 eV to the 1.6 eV bandgap of the Pb-based perovskites.<sup>10</sup> Implementing SOC significantly modifies band dispersions.<sup>9</sup>

Approaches using non-localised hybrid functionals that replace approximately 25% of DFT exchange with Hartree-Fock, improve on the LDA. The gap may be tuned with a judicious choice of parameters; however the choice of functional (*e.g.* the amount of Hartree-Fock to admix) is unclear for relatively new compounds, yet it might have a significant influence on band dispersions.

By contrast, Green's function methods, and the GW approximation in particular, are designed for excited state properties, and provide a systematically better approach to calculate quasiparticle levels. GW yields a good bandgap for MAPbI<sub>3</sub>, though there is some discrepancy among different approaches to GW. This is in part because implementations are usually LDA based (meaning *G* and *W* are calculated from DFT). Quasiparticle self-consistency in the GW context

(QSGW) removes all arbitrariness from the ambiguity in the choice of the starting Hamiltonian.<sup>11,12</sup> DFT-based GW results in a significantly narrower band gap relative to self-consistent GW. This point is often overlooked, because an additional approximation, namely the pseudo-potential approximation is widely used. It tends to overestimate gaps; when used in conjunction with DFT as a starting Hamiltonian, the two errors tend to cancel one another,<sup>13</sup> resulting in fortuitously good gaps. Moreover, errors are not systematic: the GW-LDA gaps in CuInSe<sub>2</sub>,<sup>14</sup> InN,<sup>15</sup> and NiO,<sup>16</sup> for example, are all a small fraction of actual bandgaps. QSGW is much better because, while it has a universal tendency to slightly overestimate gaps owing to ladder diagrams not included in the polarization operator, the errors are small and also highly systematic across the periodic table.<sup>12</sup> We note however, that QSGW is a very computationally expensive method which, in practice, cannot be extended to a large number of atoms.

Obtaining a bandgap showing reasonable agreement with experimental findings does not guarantee that the band dispersion is meaningful. A comparison of all the main optical features in the visible spectrum, and not only the bandgap, is useful to assess the accuracy of any method applied to a new material and has not been yet reported for MAPbI<sub>3</sub>.

Additional complexity arises from MA<sup>+</sup> being able to rotate,<sup>28–30</sup> which has been speculated to have an influence on the electronic and photo-physical properties of MAPbX<sub>3</sub>.<sup>31</sup> Molecular dynamics simulations published by Frost *et al.* suggest that MA<sup>+</sup> can align along several different preferential orientations (corresponding to the C–N axis of the molecule pointing at faces, edges or corners of the cube formed by the surrounding lead atoms).<sup>32</sup> Quasi-elastic neutron scattering measurements were shown to be compatible with MA<sup>+</sup> reorientations between these alignments with an activation energy on the order of 10 meV.<sup>30,33</sup>

Here, detailed optical characterization of MAPbX<sub>3</sub> single crystals is compared with QSGW theory to give insights into the optoelectronic properties. We show good agreement between *ab initio* QSGW simulations and single crystal ellipsometry in the spectral range containing all the visible optical transitions (1.2–5.5 eV). This enables the unambiguous assignment of the different optical features to their corresponding inter-band transition. QSGW is further used to determine the influence of cation orientation in the crystal on the optical properties of MAPbI<sub>3</sub>. Finally we use the optical data and calculations to help interpret the features of transient absorption spectra.

## Methods

### Sample preparation

Single crystals of MAPbX<sub>3</sub> were synthesized from aqueous solution based on the method described by Poglitsch and Weber.<sup>28</sup> The detailed procedure is given in the ESI Note S1.† Thin films of MAPbI<sub>3</sub> with a mirror flat surface (rms roughness <10 nm see ref. 34) were prepared from a precursor solution in a DMSO/GBL mix using the toluene method,<sup>35</sup> details of which



are also given in Note S1.† Films of sufficient quality for ellipsometry were not produced for the other halides. A description of the MAPbI<sub>3</sub> devices used for electroluminescence and sub-bandgap external quantum efficiency measurements can be found in the ESI Note S1.†

### Electroluminescence and sub-band gap external quantum efficiency

Electroluminescence (EL) was measured using a Shamrock 303 spectrograph combined with an iDUS InGaAs array detector cooled to −90 °C. EL from perovskite devices is measured at forward current densities between 1.25 and 1250 mA cm<sup>−2</sup>. The absorption coefficient is determined using the reciprocity relation between photovoltaic quantum efficiency (measured as described in the ESI Note S2†) and electroluminescent emission of solar cells, as described in ref. 36. The data was geometrically rescaled to line up on the ellipsometry data.

### Diffuse reflectance

Diffuse reflectance measurements were performed on MAPbX<sub>3</sub> single crystals crushed into a fine powder. Details of the method can be found in the ESI (Note S3).†

### Ellipsometry measurements

Spectrometric ellipsometry measurement were performed at room temperature and low humidity (<30% RH). The data on thin films was gathered using a VASE-ellipsometer from J. A. Woollam Co., Inc. equipped with Autoretarder™. Optical spectra on thin films were recorded from ca. 0.9 eV to 4.2 eV, at five incidence angles for each sample (55°, 60°, 65°, 70°, 75°).

Measurements on single crystals were performed with a SOPRALAB GES5E rotating polarizer ellipsometer mounted in a vertical configuration which is well suited for single crystals. The investigated photon energy range was from ca. 1.2 eV to 5.5 eV. Spectra were acquired at six incidence angles (55°, 60°, 65°, 67.5°, 70°, 75° for both MAPbI<sub>3</sub> and MAPbBr<sub>3</sub> and 55°, 60°, 62.5°, 65°, 70°, 75° for MAPbCl<sub>3</sub>).

### Ellipsometry fitting

Ellipsometric optical spectra are analysed using the WVASE 32 software from J. A. Woollam Co., Inc. for thin films and Winelli2 from SOPRALAB for single crystals. To fit the experimental data, an initial model of the optical transitions is built for each material constituting the sample. Any contribution other than the optical transitions is assumed to be negligible. It is apparent from eqn (1), which gives the functional form of the joint density of states (jDOS) for doubly degenerate conduction and valence band (strictly valid only for centrosymmetric crystals<sup>37</sup>), that points of reciprocal space (crystal momentum, *k*) for which valence and conduction band (with energies *E<sub>v</sub>* and *E<sub>c</sub>*) are close to parallel will substantially contribute to jDOS as the denominator in the integral will tend to zero:<sup>37</sup>

$$\text{jDOS}(E_c - E_v) = \frac{1}{4\pi^3} \int \frac{dS_k}{|\nabla_k(E_c - E_v)|}, \quad (1)$$

where *S<sub>k</sub>* is the constant energy surface defined by *E<sub>c</sub>*(*k*) − *E<sub>v</sub>*(*k*) = constant. Energies at which the jDOS is high will tend to correspond to features in the optical absorption spectrum which we model as critical points (CPs). The dielectric constant is described as the sum of critical points of the joint density of states:

$$\epsilon(E) = UV_{\text{term}} - \sum_{i=1}^N [A_i e^{j\phi_i} (E - E_{ci} + j\Gamma_i)^{n_i}] \quad (2)$$

where *N* is the number of CPs in the model. The CP *i* is described by an amplitude *A<sub>i</sub>*, energy *E<sub>ci</sub>*, linewidth *Γ<sub>i</sub>*, exciton phase angle *Φ<sub>i</sub>* and dimensionality *n<sub>i</sub>*.<sup>37</sup> A 3D CP corresponds to *n<sub>i</sub>* = 1/2. *n<sub>i</sub>* = 0 is for 2D CPs, −1/2 for 1D CPs and −1 for excitonic (0D) CPs. Details of the data fitting procedure used to derive the refractive index (*n*) and extinction coefficient (*κ*), and the effective medium model (Bruggeman) used to account for surface roughness can be found in Notes S4 and S5 in the ESI.†

### Analysing the dimensionality of the critical points

The dimensionality of the CPs is determined by fitting the second derivative of the dielectric function. This method enables the background to be removed during the fit as well as the accurate assessment of the dimensionality of the CPs. The fitted expression is therefore:<sup>38</sup>

$$\frac{d^2\epsilon}{dE^2} = \begin{cases} n_i(n_i - 1)A_i e^{j\phi_i} (E - E_{ci} + j\Gamma_i)^{n_i-2}, & n \neq 0 \\ A_i e^{j\phi_i} (E - E_{ci} + j\Gamma_i)^{-2}, & n = 0 \end{cases} \quad (3)$$

### Ab initio relativistic quasi-particle self-consistent GW calculation

The band structure discussed here is calculated from the quasiparticle self-consistent GW theory<sup>12</sup> (QSGW) implemented in an all-electron framework.<sup>11</sup> The QSGW procedure captures many-body effects and casts them optimally in an effective non-interacting Hamiltonian. Self-consistency is crucial for calculations on new materials, as it removes any ambiguity related to starting-point dependence that is problematic for the various kinds of one-shot GW implementations. Its absence has been shown to be a significant source of error for other semiconductors.<sup>12</sup>


The crystal structures were optimized with the PBEsol functional using the VASP package as previously reported.<sup>7,39</sup> Separate calculations are performed for the three local equilibrium alignments of MA C–N bonds: parallel to <100> (face), <110> (edge) and <111> (diagonal).<sup>32</sup> They provide a complete set of data for the study the impact of cation orientation on the optical properties.

The QSGW self-energy is generated using a 3 × 3 × 3 *k*-mesh. A one-shot calculation was carried out for a 4 × 4 × 4 *k*-mesh, as a perturbation to the QSGW result for the 3 × 3 × 3 case and found to increase the gap by 0.2 eV. Thus our results slightly underestimate the converged QSGW band gap. QSGW tends to overestimate the band gap by slightly more than 0.2 eV, and thus a slight overestimate relative to the experimental band gap is expected here.



Open Access Article. Published on 05 10 2015. Downloaded on 2025-05-31 1:18:36.  
This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.



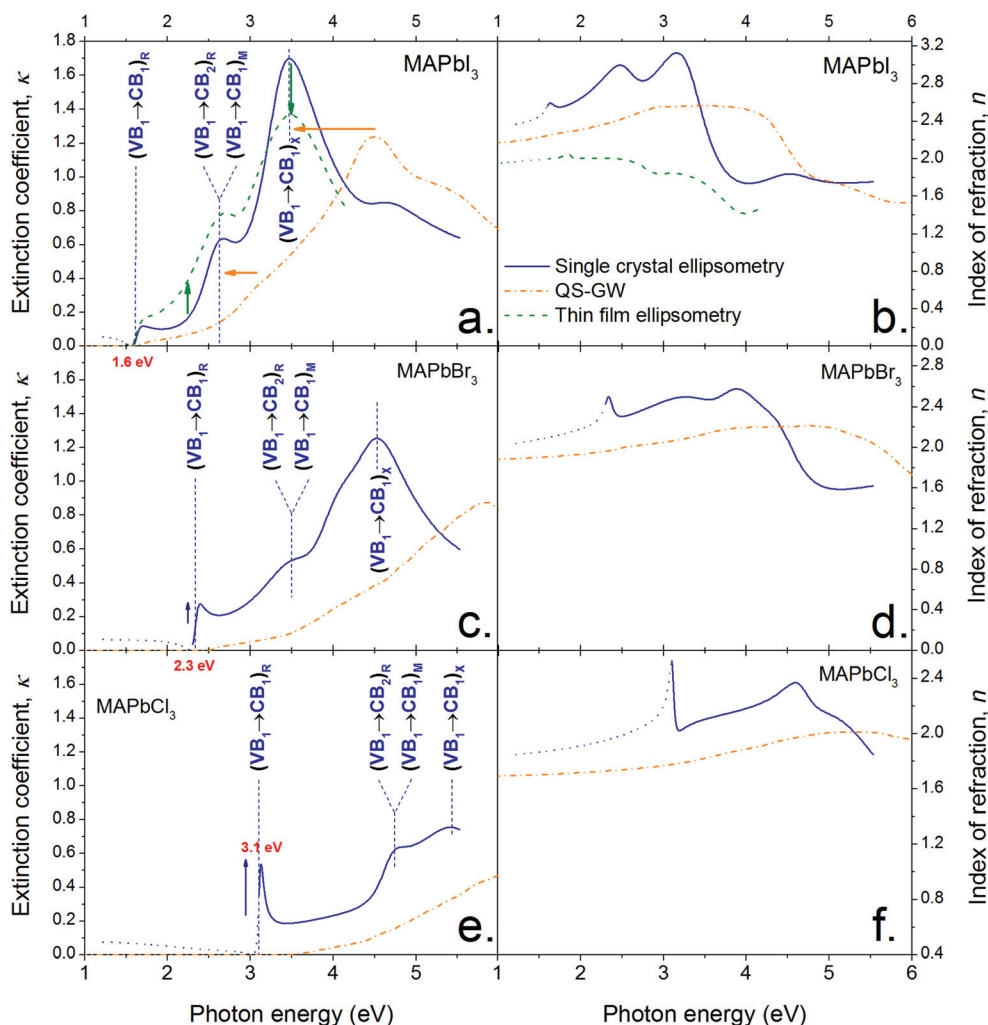

**Fig. 2** Optical constants (extinction coefficient (a, c, e) and index of refraction (b, d, f)) of  $\text{CH}_3\text{NH}_3\text{PbI}_3$  (a and b),  $\text{CH}_3\text{NH}_3\text{PbBr}_3$  (c and d) and  $\text{CH}_3\text{NH}_3\text{PbCl}_3$  (e and f) derived from single crystal ellipsometry (solid blue lines), thin film  $\text{CH}_3\text{NH}_3\text{PbI}_3$  (dashed green lines) and theory (chained orange lines, see Methods section). The three main optical features of  $\text{CH}_3\text{NH}_3\text{PbI}_3$  are assigned to the appropriate inter-band transition (VB and CB stand for 'valence band' and 'conduction band', respectively). The subscripts '1' and '2' correspond to the highest (lowest) VB (CB) or second highest (lowest) VB (CB)). The subscripts outside the brackets designate the symmetry point where the transition occurs in the first Brillouin zone, as defined in Fig. 4.

absorption edge is apparent for all materials, consistent with previous reports for  $\text{MAPbI}_3$ <sup>21</sup> and  $\text{MAPbBr}_3$ .<sup>42</sup> The values show good quantitative agreement with optical constants of thin  $\text{MAPbI}_3$  films published by Löper *et al.*<sup>18</sup> but differ from other reports<sup>3</sup> where the values may be influenced by parasitic scattering and the presence of  $\text{PbI}_2$ .

### Comparison between the different halide types


Fig. 2 shows that substituting iodide by lighter halides increases the bandgap of the compound from  $\sim 1.55$  (I) to 2.24 (Br) to 2.97 (Cl) eV (see the Tauc plots assuming direct band gap transitions obtained from diffuse reflectance measurements in Fig. 3 insets). Three main absorption peaks (corresponding to CPs) can be observed in  $\text{MAPbI}_3$  at 1.6, 2.5 and 3.1 eV. In  $\text{MAPbBr}_3$  three peaks can also be seen at  $\sim 2.3$ , 3.5 and 4.5 eV.  $\text{MAPbCl}_3$  shows only two peaks within the

measured range, at  $\sim 3.1$  and 4.6 eV (a third peak  $\sim 5.6$  eV can be distinguished slightly out of the confidence range). The absorption peak near the band gap increases in amplitude for lighter halides, as indicated by the blue arrows in Fig. 2. This behaviour is likely to be due to excitonic absorption as will be discussed further below.

### Assignment of the optical transitions

In the discussion that follows the energy bands above the band gap are referred to as  $\text{CB}_1$ ,  $\text{CB}_2$ , ..., and the energy bands below the band gap are referred to as  $\text{VB}_1$ ,  $\text{VB}_2$ , ... (see labels in Fig. 4a). A comparison between the optical constants of  $\text{MAPbI}_3$  calculated from QSGW (orange dotted line) and those obtained by ellipsometry (solid blue line) is presented in Fig. 2a and 2b. Qualitatively, both the shape and amplitude of the calculated spectra of  $n$  and  $\kappa$  show good agreement with



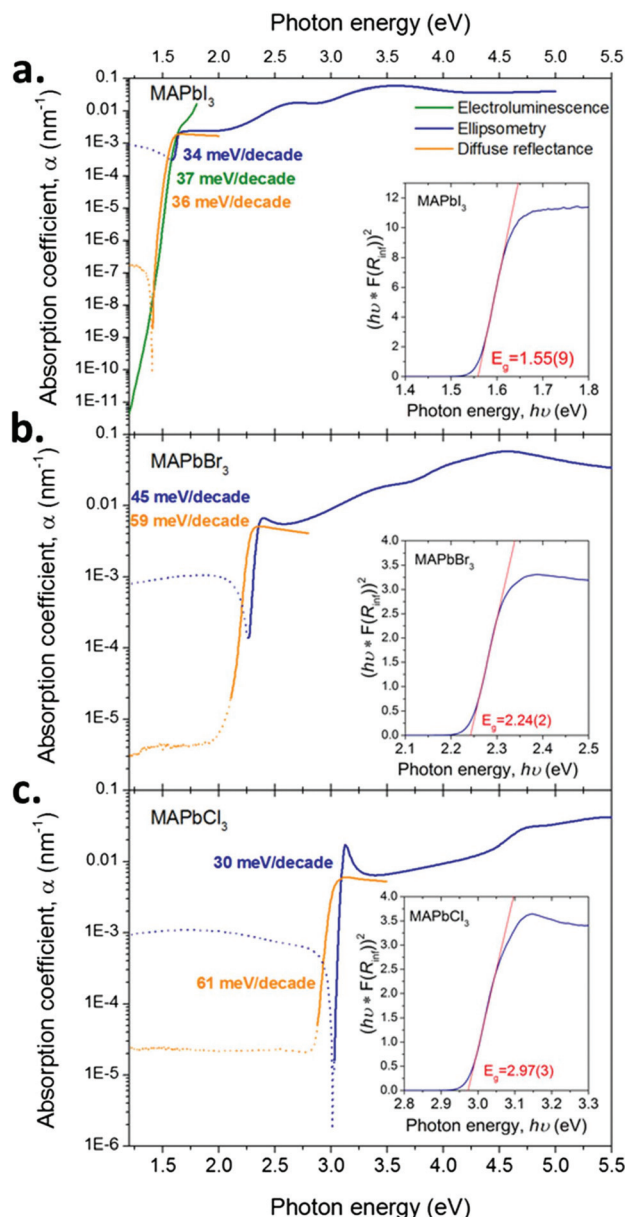


**Fig. 3** Absorption coefficient ( $\alpha = 4\pi\kappa/\lambda$ , where  $\lambda$  is the wavelength) for the three compounds (a. MAPbI<sub>3</sub>, b. MAPbBr<sub>3</sub> and c. MAPbCl<sub>3</sub>) determined by a combination of techniques: single crystal ellipsometry (solid blue line), diffuse reflectance spectroscopy (solid orange line) using single crystals crushed to a powder and electroluminescence on devices for MAPbI<sub>3</sub> (solid green line). Detail of the device architecture is given in Note S1 in the ESI.† The lines are dotted in the energy regions outside the instrument measurement capabilities. The slopes of  $d[h\nu]/d[\log_{10}(\alpha)]$  are given in the picture in a colour matching the corresponding curves. Tauc plots derived from the diffuse reflectance data are given as insets together with the estimated value of the bandgap.

experimental findings. QSGW was performed on the pseudo cubic perovskite phase. This gives a good approximation of the band structure since the transition from the tetragonal to the pseudo-cubic phase is a second order transition (unlike the 1<sup>st</sup> order orthorhombic to tetragonal transition) which results in

only a 2% change in the lattice parameters relative to the tetragonal structure at room temperature.<sup>33</sup> Thus we expect little effect of this approximation on the calculated optical constants. The predicted bandgap energy is 1.62 eV, close to the 1.5–1.6 eV obtained experimentally without the introduction of any empirical parameter. The computed and experimental extinction coefficient spectra show the same number of features in the visible spectral range. The features in the theoretical spectra are less well resolved than their experimental counterparts because the optical properties calculated for different cation alignments have been averaged and also due to the absence of electron–hole interactions in calculations as discussed below and in the Methods section. (The calculated optical constants are plotted over a larger energy range (1–10 eV) in the ESI, Fig. S6,† where each material shows the same qualitative features progressively blue shifted with decreasing radii of halide ions.) The calculated optical constants for each material also show a non-linear blue shift of the optical features relative to the experimental values – a ‘stretching’ of the curves towards higher energies. We attribute this phenomenon to the use of Random Phase Approximation (RPA) which does not account for electron–hole interactions. A better match between theory and experiment would be achieved by adding ladder diagrams to the RPA bubbles.<sup>43</sup> The additional diagrams are thought to only slightly reduce the self-energy, but they have a more pronounced effect on the dielectric function, as electron–hole pairs get attracted through the screened coulomb interaction  $W$ . This is discussed by Louie and Rohlfing in ref. 44. They show that the blue shift resulting from the omission of electron–hole interactions in GW can exceed 0.5 eV in the case of Si, while it is as high as a few eV for LiF. Unfortunately, the addition of ladder diagrams *via* a Bethe-Salpeter equation has not yet been achieved in the all-electron QSGW framework. We note that contribution of surface effects could also account for some of the observed discrepancies between observation and calculation, although we believe ignoring their effects to be less significant than the error made by using the RPA.

With this expected discrepancy taken into account, the quality of the agreement enables the unambiguous assignment of the three main optical features (labels in Fig. 2a and b) to their corresponding inter-band excitations. Fig. 4a shows the energy band diagram derived from QSGW calculations<sup>9</sup> along the relevant  $k$ -branches defined on Fig. 4b. The energy difference between conduction and valence band is plotted in Fig. 4c for different band pairs. Extrema of the curves in reciprocal space, where the conduction and valence band energies are close to parallel, correspond to CPs of the joint density of states (see eqn (1) in the Methods section). The joint density of states is the number of electronic states per unit energy and volume in the conduction and valence bands that are separated by a given photon energy taking into account spin degeneracy and selection rules. Points where the conduction and valence bands track each other (*i.e.* where the gradient  $\nabla_k(E_c - E_v)$  is minimal) dominate the dielectric function. This is replotted in Fig. 4d together with the relative contribution from different inter-band transitions.



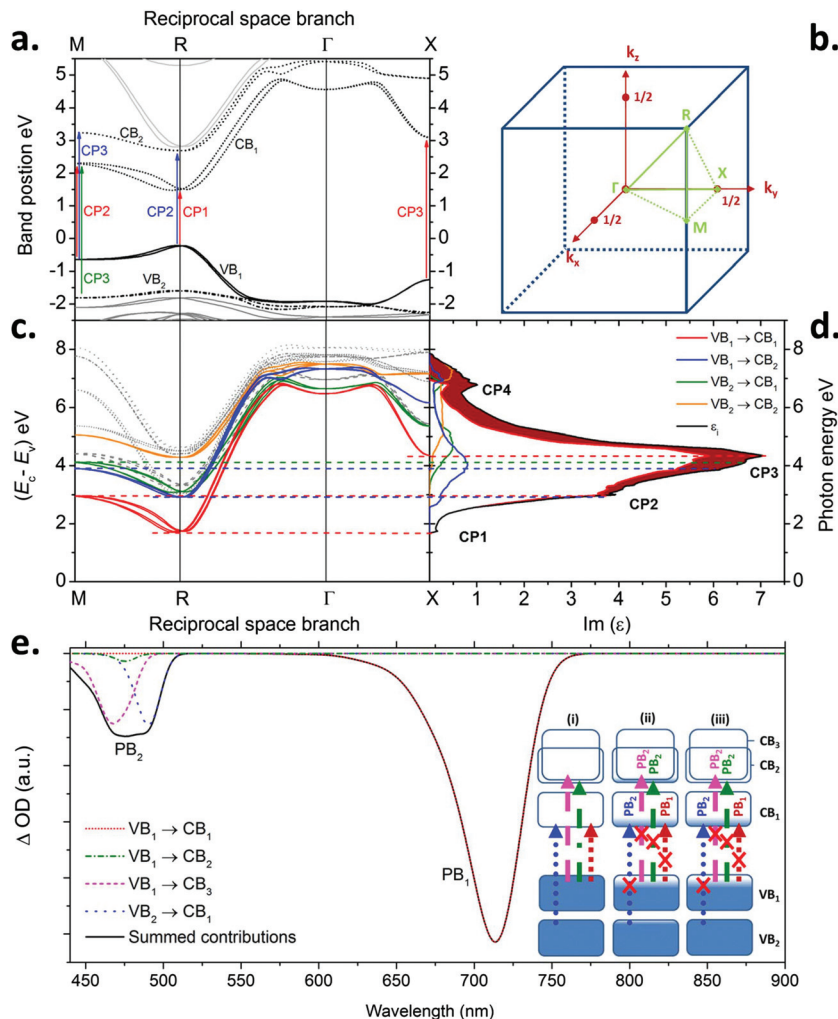

**Fig. 4** a. Energy band diagram of MAPbI<sub>3</sub> along the relevant *k*-branches in the first Brillouin zone. The labels tag the critical point transitions with the appropriate inter-band transitions (see Fig. 2) b. Schematic representation of the first Brillouin zone showing the position of the high symmetry points used in a. and c. c. Difference between conduction and valence band energy plotted for relevant band pairs. The colour code is the same as given in the inset to d. d. Imaginary part of the dielectric function (*Im*( $\epsilon$ )). The colour code helps visualizing the contributions of the different transition to *Im*( $\epsilon$ ). The area filled in dark red shows the small contribution to the imaginary part of the dielectric function from other transitions than VB<sub>1</sub> to CB<sub>1</sub>. The lines between c and d underline the correspondence between the extrema of  $E_c - E_v$  and the points of high absorption (see eqn (1) in the Methods section). e. Simulated transient absorption spectrum for a charge carrier density of  $10^{-5}$  per unit cell ( $4 \times 10^{16} \text{ cm}^{-3}$ ). The dashed black line corresponds to the summed contribution of all transitions and rescaled according to the procedure detailed in the Methods section. The main individual contributions are shown (solid coloured lines). 'PB<sub>1</sub>' and 'PB<sub>2</sub>' label the two photo-bleaches. The inset shows schematic band diagrams and optical transitions for three different scenarios: (i) no photo-excited population, (ii) photo-excited population following a pulse with energy greater than 2.6 eV (477 nm) and (iii) after excitation with a pulse energy between 1.6 and 2.5 eV (780 and 500 nm) or following relaxation of photo-excited population from (ii) within the CBs and VBs.

Inspection of Fig. 2a and 4a–d show the striking result that transitions between the highest valence band, VB<sub>1</sub>, and the lowest conduction band, CB<sub>1</sub>, are responsible for almost all the optical properties in the visible spectral range. The ellipsometry CP at the bandgap (1.62 eV, see Table S1†) is due to the inter-band transition VB<sub>1</sub> to CB<sub>1</sub> at the *R* symmetry point in the first Brillouin zone (Fig. 4b). Similarly, the second feature (modelled with a CP at 2.48 eV) involves the transition from VB<sub>1</sub> to CB<sub>1</sub> at the *M* point (with a very minor contribution from VB<sub>1</sub> to CB<sub>2</sub> at the *R* point), while the third feature (modelled

with a CP at 3.08 eV) is due to the promotion of electrons from VB<sub>1</sub> to CB<sub>1</sub> at the *X* point and also contributions from VB<sub>1</sub> to CB<sub>2</sub> and VB<sub>2</sub> to CB<sub>1</sub> around the *M* symmetry point. A similar band structure is obtained for Br- and Cl-based perovskite, as shown in Fig. S7 in the ESI.†

The sharp absorption feature observed at the band edge in all three materials may result from a discrete excitonic state enhancing absorption in this region. We reiterate that the electron–hole interaction is not accounted for in QSGW and thus cannot reproduce this feature. This may account for the much



weaker computed absorption onset around 1.6 eV. The discrepancies between optical constants determined by ellipsometry compared to the modelled ones are larger for lighter halides. This larger error is consistent with the observed increased excitonic nature of the compounds, which indicates a larger contribution of electron hole coupling on the optoelectronic properties of the compounds. Similarly the increasingly excitonic nature of the absorption edge for light halide is expected to increase the discrepancies between ellipsometry and diffuse powder reflectance results (see Fig. 3). In our ellipsometry model, the bandgap feature is modelled by one critical point only (to avoid parameter cross-correlation) whereas, physically, two features are superimposed (the onset of the joint density of states and the excitonic peak). Fitting a CP to ellipsometry data of a prominent excitonic peak at the band edge will often result in the slope of the modelled extinction coefficient *vs.* energy being steeper than in reality. This partly explains the discrepancy between the ellipsometry and diffuse reflectance measurements, additional contributions to the discrepancy are also likely to result from the change in sample morphology and surface properties when grinding the SCs to a powder.

### Properties and dimensionality of the critical points

The second derivative of the dielectric function provides insight into the dimensionality of the critical points (*cf.* Method section). The  $d^2\epsilon/dE^2$  of the three MAPbX<sub>3</sub> compounds was best fit by CPs corresponding to 0D transitions (Fig. S8–S10 and Tables S5–S7†). 0D transitions are often a characteristic of localized excitations. 0D CPs are also obtained in the case of dispersionless electron–hole states (*i.e.* where  $dE/dk \approx 0$ ). This is the case when the effective mass of both electron and hole are large (and the mobilities low since they are inversely proportional to  $d^2E/dk^2$ ) at a transition *k*-point.

The band structure in Fig. 4a shows that the bottom of the conduction band has a low curvature. This is partly because the band around the *R* point is split due to spin orbit coupling (sometimes called ‘Rashba-splitting’) resulting in a flat and non-parabolic effective dispersion.<sup>45</sup> Thus the calculated band structure is consistent with the use of a 0D critical point ellipsometry model. This observation emphasises the importance of accounting for spin–orbit coupling on the band structure dispersion of MAPbI<sub>3</sub>.

### Interpretation of transient absorption spectra

The contribution of different CB and VB and valence band pairs to the optical properties can be used to simulate transient absorption spectrum (TAS) of the material. This is achieved by calculating the difference in extinction coefficient between the semiconductor in its ground state and the case where the conduction and valence band have been respectively populated with electrons and holes from an optical pulse. The photoelectrons and holes are assumed to be thermally relaxed within their respective bands into a Fermi–Dirac distribution with a quasi-Fermi level. Fig. 4e shows a simulated transient absorption spectrum and the relative contributions from different optical transitions for an electron density of  $10^{-5}$  per

unit cell. It is calculated from the band-pair contributions to the density of states convolved with the Fermi–Dirac distributions multiplied by the corresponding optical matrix elements. To allow comparison with experiment we have shifted the energies of the transitions to correspond to the experimental wavelengths they were assigned to (see Methods section).

The simulated spectrum shows bleaching features at around 720 nm and 460 to 480 nm. These are likely to correspond to the main photo-bleach features observed experimentally at 760 nm and 480 nm.<sup>46,47</sup> Our calculations suggest that the low energy bleach is exclusively due to the population photo-generated charges in VB<sub>1</sub> and CB<sub>1</sub> at the *R* point. The second bleach at higher energy is likely to be due to a combination of inter-band transitions involving the VB<sub>1</sub> to CB<sub>2</sub>, VB<sub>2</sub> to CB<sub>1</sub> and VB<sub>1</sub> to CB<sub>3</sub> in proportions that vary depending on the density of photogenerated charge carriers (see Fig. S11 in the ESI†). This also implies that the relative magnitude of the bleach signal PB<sub>2</sub> will be greater immediately following a short wavelength excitation pulse (~400 nm) compared to excitation with a longer wavelength pulse close to the band gap. This is because directly after excitation with short wavelengths, PB<sub>2</sub> will have contributions from both the depletion of the electronic states at the top of VB<sub>1</sub> and VB<sub>2</sub> and by the filling of CB<sub>1</sub>, CB<sub>2</sub> and CB<sub>3</sub> (case ii in Fig. 4e). Thermalization of photo-excited electrons from CB<sub>3</sub> and CB<sub>2</sub> to CB<sub>1</sub>, and photo-excited holes from VB<sub>2</sub> to VB<sub>1</sub> will then occur on a picosecond time-scale (case iii in Fig. 4e). The magnitude of PB<sub>2</sub> will therefore be reduced since bleaching will arise solely from the filling of CB<sub>1</sub> and depletion of VB<sub>1</sub>. Consequently thermalization is expected to strengthen PB<sub>1</sub> relative to PB<sub>2</sub>. Our calculations show that significant contributions to PB<sub>2</sub> from VB<sub>1</sub> to CB<sub>2</sub> and CB<sub>3</sub> transitions are likely in addition to the VB<sub>2</sub> to CB<sub>1</sub> transition that has been hypothesised previously to explain the interpretation of experimental TAS spectra.<sup>46–49</sup>

The photoinduced absorption commonly measured in MAPbI<sub>3</sub> between the main photo-bleaches is not reproduced by our approach. This effect might therefore be due to (i) relaxation of the structure after excitation of a charge carrier to the CB, for example local reorientation of methylammonium cation to screen the charge that was transferred from I to Pb orbitals and/or (ii) the Stark effect.

### The influence of MA<sup>+</sup> orientation on the optical properties

We now compare the optical properties of MAPbI<sub>3</sub> for the three isotropic MA<sup>+</sup> equilibrium alignments. They correspond to MA<sup>+</sup> pointing at the face of the cube formed by the surrounding lead atoms (direction <100>, Fig. 5a), or pointing at edges (direction <110>, Fig. 5b), or along the diagonal (direction <111>, Fig. 5c).<sup>32,39</sup> In the absence of electric field or any significant interaction between the MA<sup>+</sup>, the orientational distribution determined by Frost *et al.*<sup>32</sup> is 42% along <100>, 31% along <110> and 26% along <111>.

The general aspect of the extinction coefficient (averaged in the directions of space) corresponding to the different orientations shows a similar shape over the investigated range





(1.2–5.5 eV). However, some subtle variations are of importance. Especially, different bandgaps are expected for different orientations: 1.60 eV for the  $\langle 100 \rangle$  orientation (pointing at faces), 1.46 eV for the  $\langle 110 \rangle$  (pointing at edges) and 1.52 eV in  $\langle 111 \rangle$  (pointing at corners). This result suggests that collective orientation of the dipoles in a preferential direction would result in different local bandgaps. If, as suggested previously, ferroelectric (or polarized) domains can indeed form in perovskite layers,<sup>32,50–52</sup> local variation of the optical constants are expected. The application of a sufficient electric field is therefore expected to modify the bandgap within a single crystal (or a grain). Moreover, in case of local preferential orientation, the

difference between the optical constants in the three spatial directions Fig. 5a–c will result in significant local anisotropy. The optical constants along the three directions of space in case of preferential alignment are given for MAPbBr<sub>3</sub> and MAPbCl<sub>3</sub> in the ESI Fig. S12 and S13.†


However, MA<sup>+</sup> alignment is unlikely to explain the experimental variations of the measured bandgaps in literature for MAPbI<sub>3</sub> as all of these techniques probe the macroscopic optical constants and not on the sub ~100 nm scale. The orientation of the grains is believed to be random in most cases<sup>53,54</sup> so that even when an electrical bias is applied, the macroscopic optical constants would be an average of the dominant orientations. We believe that much of the variation in the reported experimental band gaps result from differences in the details of the sample preparation, measurements and analysis.

## Conclusions

In conclusion, we have presented a precise derivation of the optical constants of MAPbI<sub>3</sub>, MAPbBr<sub>3</sub>, and MAPbCl<sub>3</sub> from single crystal varying angle spectroscopic ellipsometry on the visible part of the spectral range as well as further measurements of the optical absorption and emission of films and powders. The good agreement obtained between experimental optical constants of MAPbI<sub>3</sub> and the one derived from QSGW in the 1.2–5.5 eV range allows the unambiguous assignment of the optical features to inter-band transitions. We showed that the optical response of MAPbI<sub>3</sub> is dominated by the transition between the highest valence band the lowest conduction band, and that the contribution of other transitions is minimal due to small optical matrix elements. We have used the calculated band structure informed by our optical measurements to explain the origin of the photo-bleaching features that have been observed in transient absorption spectra. While the low energy bleach (780 nm experimentally) in the TAS seems exclusively due to the population photo-generated charges in VB<sub>1</sub> and CB<sub>1</sub> at the *R* reciprocal point, the second bleach at higher energy (480 nm) can be understood as a combination of inter-band transitions involving the VB<sub>1</sub> to CB<sub>2</sub>, VB<sub>2</sub> to CB<sub>1</sub> and VB<sub>1</sub> to CB<sub>3</sub> in proportions that vary depending on the density of photogenerated charge carriers. Previously only VB<sub>2</sub> to CB<sub>1</sub> were suggested to contribute to this bleaching. Decomposition of the QSGW results for different cation orientations shows significant differences suggesting that local preferential orientation would lead to sizeable variations of the optical properties.

## Acknowledgements

We thank Jarvist M. Frost and Paul N. Stavrinou for useful discussions, Xiao Li for assistance with sample preparation and Stefan A. Maier for access to equipment. PB and AL are grateful to the EPSRC (EP/J002305/1, EP/M014797/1 and EP/M023532/1)

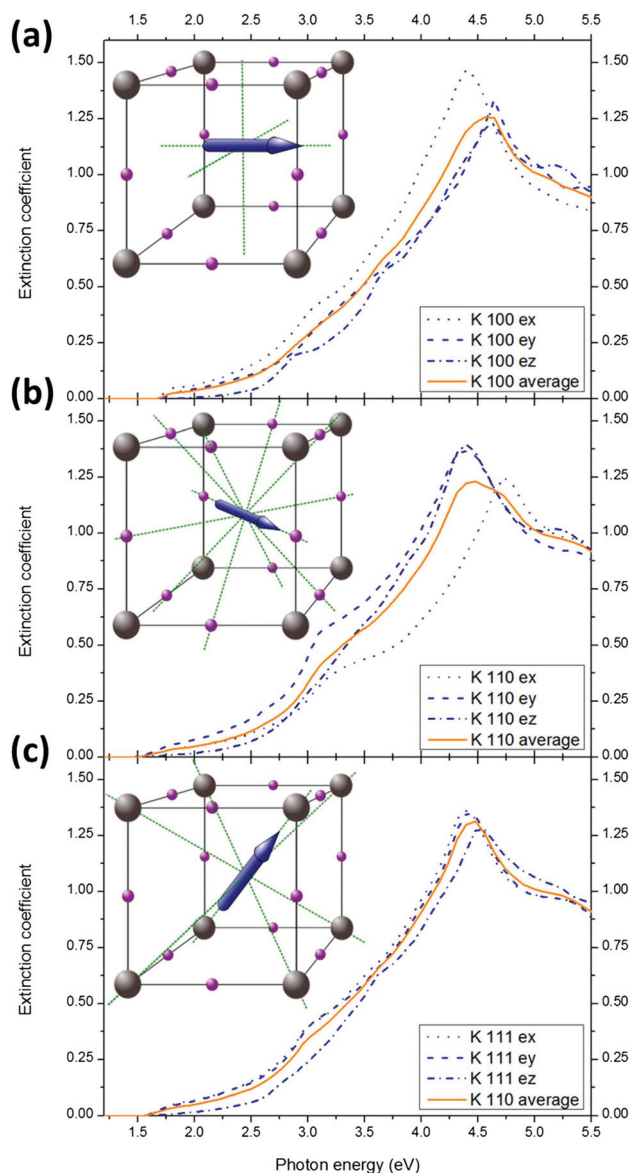

**Fig. 5** Anisotropy of calculated optical constants for the three equilibrium orientations: for MA<sup>+</sup> pointing at the faces (a), at the edges (b) and at the corners (c). An inset diagram shows one of possible orientation (blue arrow) among a set of equivalent alignments (dashed green lines).



for financial support. JN thanks the EPSRC for funding (EP/J017361 and EP/K030671/1). MCQ and MIA acknowledge financial support from MINECO through project MAT2012-37776. The theory portion of this work was supported by EPSRC (EP/M009602/1, EP/K016288/1 and EP/M009580/1).

## References

- W. Shockley and H. J. Queisser, *J. Appl. Phys.*, 1961, **32**, 510–519.
- C. Roldan-Carmona, O. Malinkiewicz, R. Betancur, G. Longo, C. Momblona, F. Jaramillo, L. Camacho and H. J. Bolink, *Energy Environ. Sci.*, 2014, **7**, 2968–2973.
- Q. Lin, A. Armin, R. C. R. Nagiri, P. Burn and P. Meredith, *Nat. Photonics*, 2015, **9**, 106–112.
- P. Hohenberg and W. Kohn, *Phys. Rev.*, 1964, **136**, B864.
- W. Kohn and L. J. Sham, *Phys. Rev.*, 1965, **140**, A1133.
- J. P. Perdew, J. A. Chevary, S. H. Vosko, K. A. Jackson, M. R. Pederson, D. J. Singh and C. Fiolhais, *Phys. Rev. B: Condens. Matter*, 1992, **46**, 6671.
- J. P. Perdew, A. Ruzsinszky, G. a. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou and K. Burke, *Phys. Rev. Lett.*, 2008, **100**, 136406.
- E. Mosconi, A. Amat, M. K. Nazeeruddin, M. Graetzel and F. De Angelis, *J. Phys. Chem. C*, 2013, **117**, 13902–13913.
- F. Brivio, K. T. Butler, A. Walsh and M. van Schilfgaarde, *Phys. Rev. B: Condens. Matter*, 2014, **89**, 155204.
- D. A. Egger and L. Kronik, *J. Phys. Chem. Lett.*, 2014, **5**, 2728–2733.
- T. Kotani, M. van Schilfgaarde and S. V. Faleev, *Phys. Rev. B: Condens. Matter*, 2007, **76**, 165106.
- M. van Schilfgaarde, T. Kotani and S. Faleev, *Phys. Rev. Lett.*, 2006, **96**, 226402.
- E. L. Shirley, X. Zhu and S. G. Louie, *Phys. Rev. B: Condens. Matter*, 1997, **56**, 6648–6661.
- J. Vidal, S. Botti, P. Olsson, J.-F. Guillemoles and L. Reining, *Phys. Rev. Lett.*, 2010, **104**, 056401.
- M. Usuda, N. Hamada, K. Shiraishi and A. Oshiyama, *Jpn. J. Appl. Phys.*, 2004, **43**, L407.
- S. V. Faleev, M. van Schilfgaarde and T. Kotani, *Phys. Rev. Lett.*, 2004, **93**, 126406.
- Y. Ogomi, A. Morita, S. Tsukamoto, T. Saitho, N. Fujikawa, Q. Shen, T. Toyoda, K. Yoshino, S. S. Pandey, T. Ma and S. Hayase, *J. Phys. Chem. Lett.*, 2014, **5**, 1004–1011.
- P. Löper, M. Stuckelberger, B. Niesen, J. Werner, M. Filipic, S.-J. Moon, J.-H. Yum, M. Topic, S. De Wolf and C. Ballif, *J. Phys. Chem. Lett.*, 2015, **6**, 66–71.
- M. M. Lee, J. Teuscher, T. Miyasaka, T. N. Murakami and H. J. Snaith, *Science*, 2012, **338**, 643–647.
- F. Hao, C. C. Stoumpos, Z. Liu, R. P. H. Chang and M. G. Kanatzidis, *J. Am. Chem. Soc.*, 2014, **136**, 16411–16419.
- T. Baikie, Y. Fang, J. M. Kadro, M. Schreyer, F. Wei, S. G. Mhaisalkar, M. Graetzel and T. J. White, *J. Mater. Chem. A*, 2013, **1**, 5628–5641.
- H.-S. Kim, C.-R. Lee, J.-H. Im, K.-B. Lee, T. Moehl, A. Marchioro, S.-J. Moon, R. Humphry-Baker, J.-H. Yum, J. E. Moser, M. Graetzel and N.-G. Park, *Sci. Rep.*, 2012, **2**, 591.
- J. M. Ball, S. D. Stranks, M. T. Horantner, S. Hüttner, W. Zhang, E. J. W. Crossland, I. Ramirez, M. Riede, M. B. Johnston, R. H. Friend and H. J. Snaith, *Energy Environ. Sci.*, 2015, **8**, 602–609.
- J. M. Ball, M. M. Lee, A. Hey and H. J. Snaith, *Environ. Sci.*, 2013, **6**, 1739.
- T. Ahmed, C. La-O-Vorakiat, T. Salim, Y. M. Lam, E. E. M. Chia and J.-X. Zhu, *EPL*, 2014, **108**, 67015.
- S. Liu, F. Zheng, N. Z. Koocher, H. Takenaka, F. Wang and A. M. Rappe, *J. Phys. Chem. Lett.*, 2015, **6**, 693–699.
- E. Mosconi, P. Umari and F. De Angelis, *J. Mater. Chem. A*, 2015, **3**, 9208–9215.
- A. Poglitsch and D. Weber, *J. Chem. Phys.*, 1987, **87**, 6373–6378.
- R. E. Wasylishen, O. Knop and J. B. Macdonald, *Solid State Commun.*, 1985, **56**, 581–582.
- A. M. A. Leguy, J. M. Frost, A. P. McMahon, V. G. Sakai, W. Kochelmann, C. Law, X. Li, F. Foglia, A. Walsh, B. C. O'Regan, J. Nelson, J. T. Cabral and P. R. F. Barnes, *Nat. Commun.*, 2015, **6**, 7124.
- J. Even, L. Pedesseau and C. Katan, *Phys. Chem. C*, 2014, **118**, 11566–11572.
- J. M. Frost, K. T. Butler and A. Walsh, *APL Mater.*, 2014, **2**, 081506–081516.
- M. T. Weller, O. J. Weber, P. F. Henry, A. M. Di Pumpo and T. C. Hansen, *Chem. Commun.*, 2015, **51**, 4180–4183.
- A. M. A. Leguy, Y. Hu, M. Campoy-Quiles, M. I. Alonso, O. J. Weber, P. Azarhoosh, M. van Schilfgaarde, M. T. Weller, T. Bein, J. Nelson, P. Docampo and P. R. F. Barnes, *Chem. Mater.*, 2015, **27**, 3397–3407.
- Z. Xiao, Q. Dong, C. Bi, Y. Shao, Y. Yuan and J. Huang, *Adv. Mater.*, 2014, **26**, 6503–6509.
- U. Rau, *Phys. Rev. B: Condens. Matter*, 2007, **76**, 085303.
- P. Y. Yu and M. Cardona, *Fundamentals of Semiconductors*, Springer-Verlag, 2001.
- P. Lautenschlager, M. Garriga, S. Logothetidis and M. Cardona, *Phys. Rev. B: Condens. Matter*, 1987, **35**, 9174–9189.
- F. Brivio, A. B. Walker and A. Walsh, *Appl. Phys. Lett.*, 2013, **1**, 042111.
- R. d. L. Kronig, *J. Opt. Soc. Am.*, 1926, **12**, 547–556.
- M. Campoy-Quiles, J. Nelson, D. D. C. Bradley and P. G. Etchegoin, *Phys. Rev. B: Condens. Matter*, 2007, **76**, 235206.
- E. Edri, S. Kirmayer, D. Cahen and G. Hodes, *J. Phys. Chem. Lett.*, 2013, **4**, 897–902.
- E. E. Salpeter and H. A. Bethe, *Phys. Rev.*, 1951, **84**, 1232–1242.
- M. Rohlfing and S. G. Louie, *Phys. Rev. B: Condens. Matter*, 2000, **62**, 4927–4944.
- F. Zheng, L. Z. Tan and A. M. Rappe, arXiv, 2015.
- J. A. Christians, J. S. Manser and P. V. Kamat, *J. Phys. Chem. Lett.*, 2015, **6**, 2086–2095.



- 47 J. S. Manser and P. V. Kamat, *Nat. Photonics*, 2014, **8**, 737–743.
- 48 G. Xing, N. Mathews, S. Sun, S. S. Lim, Y. M. Lam, M. Grätzel, S. Mhaisalkar and T. C. Sum, *Science*, 2013, **342**, 344–347.
- 49 S. D. Stranks, G. E. Eperon, G. Grancini, C. Menelaou, M. J. P. Alcocer, T. Leijtens, L. M. Herz, A. Petrozza and H. J. Snaith, *Science*, 2013, **342**, 341–344.
- 50 Y. Kutes, L. Ye, Y. Zhou, S. Pang, B. D. Huey and N. P. Padture, *J. Phys. Chem. Lett.*, 2014, **5**, 3335–3339.
- 51 C. C. Stoumpos, C. D. Malliakas and M. G. Kanatzidis, *Inorg. Chem.*, 2013, **52**, 9019–9038.
- 52 H.-S. Kim, S. K. Kim, B. J. Kim, K.-S. Shin, M. K. Gupta, H. S. Jung, S.-W. Kim and N.-G. Park, *J. Phys. Chem. Lett.*, 2015, **6**, 1729–1735.
- 53 Y. Li, J. K. Cooper, R. Buonsanti, C. Giannini, Y. Liu, F. M. Toma and I. D. Sharp, *J. Phys. Chem. Lett.*, 2015, **6**, 493–499.
- 54 T. S. Williams, F. Zuo, C.-C. Chueh, C.-Y. Liao, P.-W. Liang and A. K.-Y. Jen, *ACS Nano*, 2014, **8**, 10640–10654.

