



## Peptide-based nanomaterials for gene therapy

Cite this: *Nanoscale Adv.*, 2021, 3, 302Wei Zhang,<sup>a</sup> Qing Chen,<sup>a</sup> Feng Wu,<sup>a</sup> Jun Dai,<sup>b</sup> Defang Ding,<sup>\*a</sup> Jun Wu,<sup>b</sup> Xiaoding Lou<sup>b</sup> and Fan Xia<sup>a</sup>Received 27th October 2020  
Accepted 7th December 2020

DOI: 10.1039/d0na00899k

rsc.li/nanoscale-advances

Gene therapy is a novel therapeutic method and widely used for treating numerous diseases. However, the utilization of suitable materials for specifically and effectively delivering therapeutic oligonucleotides (ODNs) into a targeted site remains a great challenge. Regarding this, by possessing the capabilities of high loading rate, good stability, targeting ability and biological barrier penetration, peptide-based nanomaterials are developing rapidly and becoming a new trend in the application of gene therapy. In this review, a variety of peptide-based nanomaterials designed for gene therapy are briefly demonstrated, focusing on their main constituents in terms of three aspects: (1) small molecules, (2) nanoparticles and (3) polymers. Using peptide-based nanomaterials, a controlled gene delivery process can be achieved and directly monitored in a real-time mode. In future work, different designs of peptide-based nanomaterials need to be explored for higher gene transfection efficiency and a better therapeutic effect. In the end, some challenges and deficiencies are mentioned for bringing more attention to accelerate the research of peptide-based nanomaterials.

## 1 Introduction

In recent decades, gene therapy enjoyed growing interest in the field of clinical disease treatment.<sup>1–6</sup> However, because of being easily subjected to degradation and poor cellular targeting and endosome escaping abilities, direct utilization of naked therapeutic ODNs as drugs was gradually avoided.<sup>5,7,8</sup> Hence, establishing a system of selectively delivering therapeutic ODNs into targeted cells in pursuit of an effective disease therapy has drawn extensive attention.<sup>9–11</sup>

Peptides, composed of amino acid monomers with amide bonds,<sup>12,13</sup> are recognized as one group of the fundamental units to construct numerous bio-nanomaterials for applications including gene therapy.<sup>14–22</sup> By possessing different R groups, amino acids have their individual structure and function.<sup>23,24</sup> Currently, there are twenty natural amino acids and a large number of nonstandard amino acids. The combination and arrangement of different amino acids are highly diversified and varied, making the peptides rich in a variety of capabilities,<sup>25</sup> such as tissue targeting,<sup>26–28</sup> membrane penetration,<sup>29–33</sup> endosome escaping<sup>34–37</sup> and nuclear localization.<sup>38–40</sup> Moreover, functional components including luminogens and polymers are widely used to conjugate with peptides, resulting in a variety of peptide-based nanomaterials.<sup>41–47</sup> Compared with peptides without functional components, peptide-based nanomaterials

can provide more therapeutic applications.<sup>48–52</sup> For example, to achieve a high loading rate of drugs and better stability *in vivo*, the effective method is to introduce biopolymers. Herein, peptide-based nanomaterials have been largely enriched by linking with different components, which ensured specificity and selectivity and conferred satisfactory functions of gene therapy.<sup>53–58</sup>

Numerous significant studies of peptide-based nanomaterials for the purpose of gene therapy have been published recently. In this vein, we review several recent studies on peptide-based nanomaterials (Fig. 1) consisting of three different functional components including (1) small molecules, (2) nanoparticles, and (3) polymers, and focus on the design strategy for gene therapy. Finally, the difficulties and challenges



Fig. 1 Scheme of peptide-based nanomaterials for gene therapy.

<sup>a</sup>Engineering Research Center of Nano-Geomaterials of Ministry of Education, Faculty of Materials Science and Chemistry, China University of Geosciences, Wuhan 430074, China. E-mail: dingdf@cug.edu.cn; junwu@cug.edu.cn

<sup>b</sup>Department of Obstetrics and Gynecology, Tongji Hospital, Tongji Medical College, Huazhong University of Science and Technology, Wuhan 430074, China







Fig. 2 (a) Structure and function of TNCP and TNCP/ASO-NPs. (b) Transmission electron microscopy (TEM) images of  $T_D$ NCP and  $T_D$ NCP/ASO-NPs, scale bars: 200 nm. (c) Western blot of MDA-MB-231 cells incubated with different gene therapeutic agents. Reproduced with permission.<sup>113</sup> Copyright 2019 Wiley-VCH. (d) Self-assembly of the  $FC_{siRNA}$ -PyTPA complex and schematic of cellular uptake and inhibition of Bcl-2 expression. (e) TEM images of  $FC_{siRNA}$ -PyTPA and  $FC_{siRNA}$ -PyTPA incubated with CB. (f) Relative volume changes ( $V/V_0$ ) and body weight change of tumors in each group during treatment. Reproduced with permission.<sup>114</sup> Copyright 2020 Wiley-VCH.

significant specific nuclear imaging functions and tumor treatment effects, confirming the important role of small molecules in the imaging and structural self-assembly of peptide-based nanomaterials used for gene therapy.

Recently, in order to further study peptide-conjugated AIEgen nanomaterials for gene therapy, our group reported a multiple-agent-therapy probe (MATP) named  $FC_{siRNA}$ -PyTPA (Fig. 2d).<sup>114</sup>  $FC_{siRNA}$ -PyTPA was self-assembled from peptide-based molecular  $FC$ -PyTPA and siRNA, where  $FC$ -PyTPA was synthesized by conjugating small molecules  $C_{16}$  and AIEgen PyTPA with a short peptide. The short peptide was used to transport siRNA and respond to the tumor microenvironment, the amphiphilic structure with  $C_{16}$  and GGGH could self-assemble to form nanofibers and kill cancer cells and the AIEgen PyTPA was used for image-guided photodynamic therapy (PDT). When  $FC_{siRNA}$ -PyTPA reached the tumor site, MMP-2 divided  $FC_{siRNA}$ -PyTPA into  $FC_{siRNA}$  and PyTPA, which were internalized by macropinocytosis and caveolae-mediated endocytosis, respectively. Then,  $FC_{siRNA}$  entered the cells and self-assembled into nanofibers to destroy the structure of lysosomes through the reaction

of CB, which was highly expressed in lysosomes. siRNA escaped from the lysosomes and silenced the gene. At the same time, we applied light at the right time to give the PDT effect of PyTPA full play. According to TEM (Fig. 2e),  $FC_{siRNA}$  self-assembled into nanoparticles, then transformed into nanofibers under the action of CB to destroy lysosomes as shown in bio-TEM. The CLSM and absorption spectra suggested good imaging characteristics and PDT activity of PyTPA. The co-localization experiment and western blot assay indicated that siRNA was carried into the cell, where it successfully escaped from lysosomes and down-regulated the expression of Bcl-2 to promote cancer cell death. Finally, the triple combination therapy successfully down-regulated the expression of anti-apoptotic proteins and effectively inhibited tumor growth (Fig. 2f). This work showed us that by combining small molecules with functional peptides, siRNA can be effectively transported, and also proved the important role of peptide-based nanomaterials in gene therapy and multiple therapy.

There are also other small molecules used in peptide-based nanomaterials to promote structural self-assembly and for





gene therapy. For example, Kostarelos and his co-workers<sup>53</sup> designed self-assembled peptide nanofibers (PNFs) composed of palmitoyl and a peptide (GGGAAAKRK), which could deliver siRNA and silence the target Bcl-2 in specific loci of the brain. Liu and co-workers<sup>115</sup> combined a stearyl segment that self-assembled inside the structure in an aqueous environment with peptide to construct an  $\alpha$ -helical structure and promote hydrophobic interactions with the cell membrane, which led to the improvement of gene transfection efficiency.


### 3.2 Nanoparticles

Nanoparticles such as gold nanoparticles (AuNPs), nanodiamonds (NDs), and porous silicon nanoparticles are widely studied because of their special physical and chemical properties, such as easy surface functionalization, good stability and easy size control, so they are often used in the field of gene therapy.<sup>116–118</sup> When a peptide is combined with nanoparticles, it can improve the targeting ability of nanomaterials, reduce the biological toxicity and improve the therapeutic effect.

AuNPs are some of the promising nanoparticles as they are nontoxic and can be easily modified on the surface or a good single nanoparticle carrier.<sup>119–121</sup> As gold has been approved by the FDA for preclinical trials, gene modification of rat mesenchymal stem cells (rMSC) with AuNPs is expected to generate therapeutic cell lines. Strouse and co-workers<sup>122</sup> designed a solid gold nanoparticle AuNP-complex for delivering genes into mesenchymal stem cells (MSC) (Fig. 3a). The surface of AuNPs was modified with a BDNF/mCherry fusion gene (6.6 kbp), which could express the BDNF/mCherry fusion protein, and a Ku70 peptide whose N-terminal was modified with

cysteine through thiol linkage chemistry to form the AuNP-complex of about 130 nm (Fig. 3b). The Ku70 peptide is an intriguing pentapeptide from Ku70 which is a DNA repair binding sequence and plays a role in antiapoptosis. What's more, the N-terminal cysteine modified Ku70 peptide is zwitterionic and reduces electrostatic interactions between the BDNF/mCherry fusion gene and AuNP peptide surface which is effective for improving nanoparticle's gene transfection. According to the calculated loading level of the peptide per AuNP, a value of 3.6 ligands per nm<sup>2</sup> was obtained. The optical images showed that more than 80% of rMSC cells expressed after transfection with the AuNP-complex within 4 days, and a Cedex Cell Counter and analyzer system showed that 98.3% of rMSC cells survived after single transfection, which indicated that the gene transfection of MSC population was successfully achieved by using the AuNP-complex with no significant effects on downstream of the MSCs. And the western blot analysis showed that the expression of BDNF protein was time-dependent in the media after gene transfection (Fig. 3c). This study established a new method to transfect the BDNF/mCherry fusion gene and proved that AuNPs modified by a gene and Ku70 peptide can effectively change the protein expression of MSCs and induce one-step transformation of rMSCs, while avoiding an apoptotic response.

The NDs are attractive because of their long-term particle tracking *in vivo* and fluorescence cell labelling/imaging *in vitro* with no inflammatory indications and no immune response in animal models.<sup>123–125</sup> Lo and co-workers<sup>126</sup> reported cationic peptide-functionalized NDs to enhance cellular uptake and deliver loaded antisense ODNs to the nucleus (Fig. 3d). The 30 nm NDs were modified with dual-function, cationic TAT-NLS

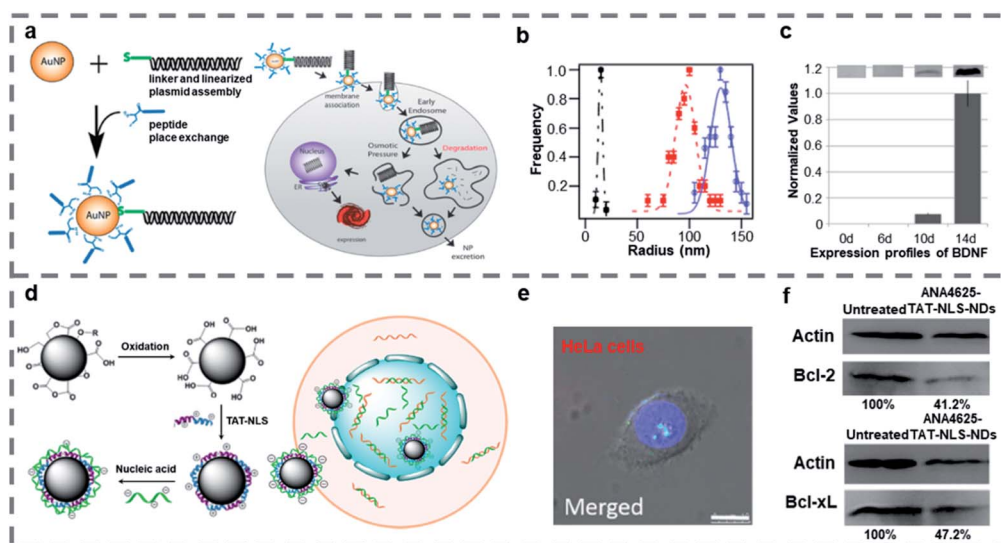

**Fig. 3** (a) Assembly of the AuNP-complex, the fusion gene and schematic of cellular uptake of the AuNP-complex and subsequent exogenous BDNF/mCherry protein expression. (b) Dynamic light scattering data for the AuNP-gene (blue, 130 nm), the linearized gene (red, 97 nm), and 6.6 nm water-soluble BSP-AuNPs (black, 15 nm). (c) Time-dependent secretion levels for BDNF expression determined using western blot analysis. Reproduced with permission.<sup>122</sup> Copyright 2014 American Chemical Society. (d) Synthetic scheme of TAT-NLS-NDs and cargo-loaded TAT-NLS-NDs and schematic of cargo-loaded TAT-NLS-NDs entering cells and nucleus. (e) CLSM of ANA4625-Cy3-TAT-NLS-NDs (red) in HeLa cells stained with Hoechst (blue), scale bar: 10  $\mu$ m. (f) Western blot analysis of Bcl-2 and Bcl-xL expressions in MCF-7 cells after treatment with or without ANA4625-TAT-NLS NDs. Reproduced with permission.<sup>126</sup> Copyright 2018 American Chemical Society.





were designed to deliver cisplatin, which improved the effects of the circulation *in vivo* of cisplatin.<sup>142,143</sup> What's more, inhibition of autophagy may reduce the resistance of tumor cells to cisplatin.<sup>144</sup> Wang and co-workers<sup>145</sup> developed a self-assembled nanoprodru platform named siBec1@PPN containing cisplatin and Beclin1 RNAi (siBec1 is an autophagy initiation factor), which could inhibit the growth of the cisplatin-resistant tumor. The nanoprodru platform was self-assembled using three parts including Pt(IV)-peptide-bis(pyrene), DSPE-PEG and cRGD-modified DSPE-PEG (Fig. 4d). The Pt(IV)-peptide-bis(pyrene) loaded Pt(IV) with a load rate up to 95%, released Pt(II) in the presence of glutathione (GSH) and delivered siBec1 into the cytoplasm, which inhibited autophagy and increased the cell apoptosis. The DSPE-PEG increased the stability and biocompatibility of the nanoparticles and the cRGD helped nanoparticles to target the tumor cells. As TEM images (Fig. 4e) show, the siBec1@PPN is a spherical structure with a size of  $54.44 \pm 11.13$  nm. What's more, the western blot (Fig. 4f) showed that the siBec1 was transfected successfully and it inhibited the Beclin1 expression on A549 tumor cells. Animal study results showed that the siBec1@PPN reversed Pt resistance by siBec1-mediated autophagy inhibition and the tumor cells were apoptotic. Overall, siBec1@PPN showed us the ability of peptide-polymer complexes to transfer genes effectively and inhibit the growth of tumor cells.

Due to the excellent properties of polymers, a large number of studies have been carried out. For example, Rosenecker and co-workers<sup>146</sup> developed compact and monodisperse peptide-polyoxamine nanoparticles, which could long-term repair the cystic fibrosis transmembrane conductance regulator defect *in vitro* and *in vivo* with a safe profile. Wang and co-workers<sup>147</sup> reported that polyurethane nanomicelles modified by an osteoblast-targeting peptide could selectively target osteoblasts to deliver siRNA/microRNA without overt toxicity or causing an immune response *in vivo*.

## 4 Conclusions

In this review, several peptide-based nanomaterials self-assembled from peptides and three individual functional components are introduced for the application of gene therapy. Compared with pure peptide sequences, peptide-based nanomaterials with other functional components appear to be more ideal gene delivery materials by taking advantage of multifunctionality, good biocompatibility, high load rate *etc.* In order to improve the specific targeting and transfection efficiency for gene therapy and add additional features to the design, more details but not limited to the following issues need to be considered: (1) the design of small molecule-peptide nanomaterials requires rational selection of suitable functional polypeptides and small molecules, in terms of the length, electrical properties, hydrophilicity and hydrophobicity of peptides and structures of small molecules, to avoid the interference between peptides and small molecules; (2) there is room for improvement of preparation of nanoparticle-peptide nanomaterials to enhance the homogeneity of products and reduce the side effects *in vivo*; (3) the non-specific adsorption of

polymers could be further eliminated, and accelerating the targeting of polymer-peptide nanomaterials to tumor cells would be more favored; (4) the design strategy of peptide-based materials such as the load part of ODNs, biological functional peptides, the ratio of peptides and other components and the self-assembly structure should be considered. However, peptide-based nanomaterials used in gene therapy still have some problems such as poor structural stability in serum, being easily degraded *in vivo* and low gene loading rate. What's more, the combination of peptides with other components without affecting the function of each part is still a problem to be solved. In the future, it is necessary to study the secondary structure of peptides in depth and to improve the circulation time *in vivo* and the accumulation of peptide-based nanomaterials in the target tissue for clinical use. And the applications of peptide-based nanomaterials in other fields, such as cancer treatment, bioimaging, and tissue biomaterial engineering, need to be further studied.

On the basis of notable achievements, peptide-based nanomaterials will be developed with more novel and efficient designs in the near future. In order to obtain advanced functional peptide-based nanomaterials, for example, it is necessary to explore the complex structure of peptides containing unnatural amino acids and optimize multifunctional components to ensure their precise functions. Because of the space limitation, this review is confined to three components (small molecules, nanoparticles, and polymers) which construct peptide-based nanomaterials. However, we hope that it will be able to promote the research of peptide-based nanomaterials for gene therapy and accelerate their development in the fields of nanomaterials, biology and chemistry.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work is supported by the National Key R&D Program of China (2020YFA0211200), the National Natural Science Foundation of China (21722507, 21525523, 21974128, 21874121 and 21802130), the Natural Science Foundation of Hubei Province (2019CFA043), the project funded by the China Postdoctoral Science Foundation (2020M672436), the Open Research Fund of State Key Laboratory of Bioelectronics, Southeast University, and the Hubei Postdoctoral Innovative Research Foundation (to Jun Wu).

## Notes and references

- O. Khorkova and C. Wahlestedt, *Nat. Biotechnol.*, 2017, **35**, 249–263.
- M. Matsui and D. R. Corey, *Nat. Rev. Drug Discovery*, 2017, **16**, 167–179.
- A. Wittrup and J. Lieberman, *Nat. Rev. Genet.*, 2015, **16**, 543–552.





- 4 C. E. Dunbar, K. A. High, J. K. Joung, D. B. Kohn, K. Ozawa and M. Sadelain, *Science*, 2018, **359**, eaan4672.
- 5 S. F. Dowdy, *Nat. Biotechnol.*, 2017, **35**, 222–229.
- 6 M. Wang, Z. A. Glass and Q. Xu, *Gene Ther.*, 2017, **24**, 144–150.
- 7 K. A. Whitehead, R. Langer and D. G. Anderson, *Nat. Rev. Drug Discovery*, 2009, **8**, 129–138.
- 8 J. Chen, L. Lin, Z. P. Guo, C. N. Xu, H. Y. Tian, K. Park and X. S. Chen, *J. Drug Deliv. Sci. Technol.*, 2015, **30**, 417–423.
- 9 D. Ibraheem, A. Elaissari and H. Fessi, *Int. J. Pharm.*, 2014, **459**, 70–83.
- 10 M. R. Molla and P. A. Levkin, *Adv. Mater.*, 2016, **28**, 1159–1175.
- 11 H. J. Kim, A. Kim, K. Miyata and K. Kataoka, *Adv. Drug Delivery Rev.*, 2016, **104**, 61–77.
- 12 G. Qi, Y. Gao, L. Wang and H. Wang, *Adv. Mater.*, 2018, **30**, 1703444.
- 13 C. Zhang, W. Wu, R. Li, W. Qiu, Z. Zhuang, S. Cheng and X. Zhang, *Adv. Funct. Mater.*, 2018, **28**, 1804492.
- 14 C. D. Fjell, J. A. Hiss, R. E. Hancock and G. Schneider, *Nat. Rev. Drug Discovery*, 2012, **11**, 37.
- 15 M. Shadidi and M. Sioud, *Drug Resist. Updates*, 2003, **6**, 363.
- 16 P. Vlieghe, V. Lisowski, J. Martinez and M. Khrestchatsky, *Drug Discovery Today*, 2010, **15**, 40.
- 17 M. Abbas, Q. Zou, S. Li and X. Yan, *Adv. Mater.*, 2017, **29**, 201605021.
- 18 K. S. Lam, S. E. Salmon, E. M. Hersh, V. J. Hruby, W. M. Kazmierski and R. J. Knapp, *Nature*, 1991, **354**, 82.
- 19 P. Midoux, C. Pichon, J. Yaouanc and P. Jaffrès, *Br. J. Pharmacol.*, 2009, **157**, 166–178.
- 20 M. E. Martin and K. G. Rice, *AAPS J.*, 2007, **9**, E18–E29.
- 21 H. Wang, Z. Feng and B. Xu, *Theranostics*, 2019, **9**, 3212–3222.
- 22 J. Hoyer and I. Neundorff, *Acc. Chem. Res.*, 2012, **45**, 1048–1056.
- 23 R. V. Ulijn and A. M. Smith, *Chem. Soc. Rev.*, 2008, **37**, 664–675.
- 24 A. Kidera, Y. Konishi, M. Oka, T. Ooi and H. A. Scheraga, *J. Protein Chem.*, 1985, **4**, 23–55.
- 25 Z. Kang, Q. Meng and K. Liu, *J. Mater. Chem. B*, 2019, **7**, 1824–1841.
- 26 W. Wang and Z. Hu, *Adv. Mater.*, 2019, **31**, 1804827.
- 27 S. Lee, J. Xie and X. Chen, *Biochemistry*, 2010, **49**, 1364–1376.
- 28 F. Araste, K. Abnous, M. Hashemi, S. M. Taghdisi, M. Ramezani and M. Alibolandi, *J. Controlled Release*, 2018, **292**, 141–162.
- 29 M. Green, M. Ishino and P. M. Loewenstein, *Cell*, 1989, **58**, 215–223.
- 30 P. Lundberg and Ü. Langel, *J. Mol. Recognit.*, 2003, **16**, 227–233.
- 31 J. Temsamani and P. Vidal, *Drug Discovery Today*, 2004, **9**, 1012–1019.
- 32 T. Lehto, K. Ezzat, M. J. Wood and S. E. Andaloussi, *Adv. Drug Delivery Rev.*, 2016, **106**, 172–182.
- 33 N. Nakayama, S. Takaoka, M. Ota, K. Takagaki and K. I. Sano, *Langmuir*, 2018, **34**, 14286–14293.
- 34 P. Midoux and M. Monsigny, *Bioconjugate Chem.*, 1999, **10**, 406–411.
- 35 S. L. Lo and S. Wang, *Biomaterials*, 2008, **29**, 2408–2414.
- 36 K. A. Brogden, *Nat. Rev. Microbiol.*, 2005, **3**, 238–250.
- 37 J. G. Schellinger, J. A. Pahang, R. N. Johnson, D. S. H. Chu, D. L. Sellers, D. O. Maris, A. J. Convertine, P. S. Stayton, P. J. Horner and S. H. Pun, *Biomaterials*, 2013, **34**, 2318–2326.
- 38 M. van der Aa, E. Mastrobattista, R. S. Oosting, W. E. Hennink, G. A. Koning and D. J. A. Crommelin, *Pharm. Res.*, 2006, **23**, 447–459.
- 39 J. Robbins, S. M. Dilworth, R. A. Laskey and C. Dingwall, *Cell*, 1991, **64**, 615–623.
- 40 Y. Y. Xu, W. L. Liang, Y. S. Qiu, M. Cespi, G. F. Palmieri, A. J. Mason and J. K. W. Lam, *Mol. Pharm.*, 2016, **13**, 3141–3152.
- 41 T. Jiang, T. A. Meyer, C. Modlin, X. Zuo, V. P. Conticello and Y. Ke, *J. Am. Chem. Soc.*, 2017, **139**, 14025–14028.
- 42 A. T. Preslar, G. Parigi, M. T. McClendon, S. S. Sefick, T. J. Moyer, C. R. Haney, E. A. Waters, K. W. MacRenaris, C. Luchinat and S. I. Stupp, *ACS Nano*, 2014, **8**, 7325.
- 43 S. Silva, A. J. Almeida and N. Vale, *Biomolecules*, 2019, **9**, 22.
- 44 G. Wei, Y. Wang, X. Huang, H. Hou and S. Zhou, *Small Methods*, 2018, **2**, 1700358.
- 45 J. Y. Shu, B. Panganiban and T. Xu, *Annu. Rev. Phys. Chem.*, 2013, **64**, 631–657.
- 46 J. Couet, J. D. J. S. Samuel, A. Kopyshchev, S. Santer and M. Biesalski, *Angew. Chem., Int. Ed.*, 2005, **44**, 3297–3301.
- 47 D. Zaramella, P. Scrimin and L. J. Prins, *J. Am. Chem. Soc.*, 2012, **134**, 8396–8399.
- 48 L. Zhang, D. Jing, N. Jiang, T. Rojalin, C. M. Baehr, D. Zhang, W. Xiao, Y. Wu, Z. Cong, J. J. Li, Y. Li, L. Wang and K. S. Lam, *Nat. Nanotechnol.*, 2020, **15**, 145–153.
- 49 Q. Luo, Y. Lin, P. Yang, Y. Wang, G. Qi, Z. Qiao, B. Li, K. Zhang, J. Zhang, L. Wang and H. Wang, *Nat. Commun.*, 2018, **9**, 1802.
- 50 K. Han, W. Zhang, J. Zhang, Q. Lei, S. Wang, J. Liu, X. Zhang and H. Han, *Adv. Funct. Mater.*, 2016, **26**, 4351–4361.
- 51 H. Wang, Z. Feng, W. Tan and B. Xu, *Bioconjugate Chem.*, 2019, **30**, 2528–2532.
- 52 G. Qi, F. Hu, Kenry, L. Shi, M. Wu and B. Liu, *Angew. Chem., Int. Ed.*, 2019, **58**, 16229–16235.
- 53 M. Mazza, M. Hadjidemetriou, I. de Lázaro, C. Bussy and K. Kostarelos, *ACS Nano*, 2015, **9**, 1137–1149.
- 54 Y. Ruff, T. Moyer, C. J. Newcomb, B. Demeler and S. I. Stupp, *J. Am. Chem. Soc.*, 2013, **135**, 6211–6219.
- 55 H. Yin, R. L. Kanasty, A. A. Eltoukhy, A. J. Vegas, J. R. Dorkin and D. G. Anderson, *Nat. Rev. Genet.*, 2014, **15**, 541–555.
- 56 T. Fan, X. Yu, B. Shen and L. Sun, *J. Nanomater.*, 2017, **2017**, 4562474.
- 57 R. Kedmi, N. Veiga, S. Ramishetti, M. Goldsmith, D. Rosenblum, N. Dammes, I. Hazan-Halevy, L. Nahary, S. Leviatan-Ben-Arye, M. Harlev, M. Behlke, I. Benhar, J. Lieberman and D. Peer, *Nat. Nanotechnol.*, 2018, **13**, 214–219.
- 58 Li. Liu, Z. Li, L. Rong, S. Qin, Q. Lei, H. Cheng, X. Zhou, R. Zhuo and X. Zhang, *ACS Macro Lett.*, 2014, **3**, 467–471.



- 59 C. Y. Yu, Z. Yuan, Z. Cao, B. Wang, C. Qiao, J. Li and X. Xiao, *Gene Ther.*, 2009, **16**, 953–962.
- 60 S. Kasugai, R. Fujisawa, Y. Waki, K. I. Miyamoto and K. Ohya, *J. Bone Miner. Res.*, 2000, **15**, 936–943.
- 61 Y. Dong, T. Yu, L. Ding, E. Laurini, Y. Huang, M. Zhang, Y. Weng, S. Lin, P. Chen, D. Marson, Y. Jiang, S. Giorgio, S. Princl, X. Liu, P. Rocchi and L. Peng, *J. Am. Chem. Soc.*, 2018, **140**, 16264–16274.
- 62 Y. Liu, L. Mei, C. Xu, Q. Yu, K. Shi, L. Zhang, Y. Wang, Q. Zhang, H. Gao, Z. Zhang and Q. He, *Theranostics*, 2016, **6**, 177–191.
- 63 C. Mas-Moruno, R. Fraioli, F. Rechenmacher, S. Neubauer, T. G. Kapp and H. Kessler, *Angew. Chem., Int. Ed.*, 2016, **55**, 7048–7067.
- 64 S. R. Kumar, F. A. Gallazzi, R. Ferdani, C. J. Anderson, T. P. Quinn and S. L. Deutscher, *Cancer Biother. Radiopharm.*, 2010, **25**, 693–703.
- 65 S. R. Kumar, T. P. Quinn and S. L. Deutscher, *Clin. Cancer Res.*, 2007, **13**, 6070–6079.
- 66 H. M. Ellerby, W. Arap, L. M. Ellerby, R. Kain, R. Andrusiak, G. D. Rio, S. Krajewski, C. R. Lombardo, R. Rao, E. Ruoslahti, D. E. Bredesen and R. Pasqualini, *Nat. Med.*, 1999, **5**, 1032–1038.
- 67 K. Han, Q. Lei, S. B. Wang, J. J. Hu, W. X. Qiu, J. Y. Zhu, W. N. Yin, X. Luo and X. Z. Zhang, *Adv. Funct. Mater.*, 2015, **25**, 2961–2971.
- 68 L. Agemy, D. Friedmann-Morvinski, V. R. Kotamraju, L. Roth, K. N. Sugahara, O. M. Girard, R. F. Mattrey, I. M. Verma and E. Ruoslahti, *Proc. Natl. Acad. Sci. U. S. A.*, 2011, **108**, 17450–17455.
- 69 Z. Y. Qiao, Y. X. Lin, W. J. Lai, C. Y. Hou, Y. Wang, S. L. Qiao, D. Zhang, Q. J. Fang and H. Wang, *Adv. Mater.*, 2016, **28**, 1859–1867.
- 70 A. D. Frankel and C. O. Pabo, *Cell*, 1988, **55**, 1189–1193.
- 71 S. Y. Li, H. Cheng, W. X. Qiu, L. H. Liu, S. Chen, Y. Hu, B. R. Xie, B. Li and X. Z. Zhang, *ACS Appl. Mater. Interfaces*, 2015, **7**, 28319–28329.
- 72 Y. Cheng, F. Huang, X. Min, P. Gao, T. Zhang, X. Li, B. Liu, Y. Hong, X. Lou and F. Xia, *Anal. Chem.*, 2016, **88**, 8913–8919.
- 73 K. N. Sugahara, P. Scodeller, G. B. Braun, T. H. de Mendoza, C. M. Yamazaki, M. D. Kluger, J. Kitayama, E. Alvarez, S. B. Howell, T. Teesalu, E. Ruoslahti and A. M. Lowy, *J. Controlled Release*, 2015, **212**, 59–69.
- 74 S. F. Ye, M. M. Tian, T. X. Wang, L. Ren, D. Wang, L. H. Shen and T. Shang, *Nanomed. Nanotechnol. Biol. Med.*, 2012, **8**, 833–841.
- 75 N. K. Subbarao, R. A. Parente, F. C. Szoka Jr, L. Nadasdi and K. Pongracz, *Biochemistry*, 1987, **26**, 2964–2972.
- 76 D. Calderon, W. D. Richardson, A. F. Markham and A. E. Smith, *Nature*, 1984, **311**, 33–38.
- 77 D. Calderon and A. E. Smith, *Virology*, 1984, **139**, 109–137.
- 78 B. K. Kim, H. Kang, K. O. Doh, S. H. Lee, J. W. Park, S. J. Lee and T. J. Lee, *Bioorg. Med. Chem. Lett.*, 2012, **22**, 5415–5418.
- 79 A. Leonidova, V. Pierroz, R. Rubbiani, Y. Lan, A. G. Schmitz, A. Kaech, R. K. O. Sigel, S. Ferrari and G. Gasser, *Chem. Sci.*, 2014, **5**, 4044–4056.
- 80 Y. Liu, D. Zhang, Z. Y. Qiao, G. B. Qi, X. J. Liang, X. G. Chen and H. Wang, *Adv. Mater.*, 2015, **27**, 5034–5042.
- 81 P. D. Nguyen, V. T. Cong, C. Baek and J. Min, *Biosens. Bioelectron.*, 2017, **89**, 666–672.
- 82 L. I. Fessler, K. G. Duncan, J. H. Fessler, T. Salo and K. Tryggvason, *J. Biol. Chem.*, 1984, **259**, 9783–9789.
- 83 Y. Lu, W. Sun and Z. Gu, *J. Controlled Release*, 2014, **194**, 1–19.
- 84 W. Song, J. Kuang, C. X. Li, M. K. Zhang, D. W. Zheng, X. Zeng, C. J. Liu and X. Z. Zhang, *ACS Nano*, 2018, **12**, 1978–1989.
- 85 Y. Yuan, C. J. Zhang, M. Gao, R. Zhang, B. Z. Tang and B. Liu, *Angew. Chem., Int. Ed.*, 2015, **54**, 1780–1786.
- 86 M. Gao and B. Z. Tang, *Coord. Chem. Rev.*, 2020, **402**, UNSP 213076.
- 87 Z. Zhao, H. Zhang, J. W. Y. Lam and B. Z. Tang, *Angew. Chem., Int. Ed.*, 2020, **59**, 9888–9907.
- 88 D. Wang and B. Z. Tang, *Acc. Chem. Res.*, 2019, **52**, 2559–2570.
- 89 H. W. Liu, L. Chen, C. Xu, Z. Li, H. Zhang, X. B. Zhang and W. Tan, *Chem. Soc. Rev.*, 2018, **47**, 7140–7180.
- 90 X. Wu, W. Shi, X. Li and H. Ma, *Acc. Chem. Res.*, 2019, **52**, 1892–1904.
- 91 S. Ding and Y. Hong, *Chem. Soc. Rev.*, 2020, **49**, 8354–8389.
- 92 R. A. Petros and J. M. DeSimone, *Nat. Rev. Drug Discovery*, 2010, **9**, 615–627.
- 93 A. Nel, T. Xia, L. Mdlar and N. Li, *Science*, 2006, **311**, 622–627.
- 94 I. W. Hamley, *Chem. Rev.*, 2017, **117**, 14015–14041.
- 95 D. Ding, K. Li, B. Liu and B. Z. Tang, *Acc. Chem. Res.*, 2013, **46**, 2441–2453.
- 96 J. Mei, Y. Huang and H. Tian, *ACS Appl. Mater. Interfaces*, 2018, **10**, 12217–12261.
- 97 J. Luo, Z. Xie, J. W. Y. Lam, L. Cheng, H. Chen, C. Qiu, H. S. Kwok, X. Zhan, Y. Liu, D. Zhu and B. Z. Tang, *Chem. Commun.*, 2001, 1740–1741.
- 98 X. Wang, J. Dai, X. Min, Z. Yu, Y. Cheng, K. Huang, J. Yang, X. Yi, X. Lou and F. Xia, *Anal. Chem.*, 2018, **90**, 8162–8169.
- 99 Y. Cheng, J. Dai, C. Sun, R. Liu, T. Zhai, X. Lou and F. Xia, *Angew. Chem., Int. Ed.*, 2018, **57**, 3123–3127.
- 100 R. Hu, B. Chen, Z. Wang, A. Qin, Z. Zhao, X. Lou and B. Z. Tang, *Biomaterials*, 2019, **203**, 43–51.
- 101 X. Ni, X. Zhang, X. Duan, H. Zheng, X. Xue and D. Ding, *Nano Lett.*, 2019, **19**, 318–330.
- 102 X. Xu, W. Zhao, P. Gao, H. Li, G. Feng and X. Lou, *NPG Asia Mater.*, 2016, **8**, e234.
- 103 Z. Long, S. Zhan, P. Gao, Y. Wang, X. Lou and F. Xia, *Anal. Chem.*, 2018, **90**, 577–588.
- 104 J. Dai, Y. Li, Z. Long, R. Jiang, Z. Zhuang, Z. Wang, Z. Zhao, X. Lou, F. Xia and B. Z. Tang, *ACS Nano*, 2020, **14**, 854–866.
- 105 X. Yi, J. Dai, Y. Han, M. Xu, X. Zhang, S. Zhen, Z. Zhao, X. Lou and F. Xia, *Commun. Biol.*, 2018, **1**, 202.
- 106 C. Chen, X. Ni, S. Jia, Y. Liang, X. Wu, D. Kong and D. Ding, *Adv. Mater.*, 2019, **31**, 1904914.
- 107 C. Chen, H. Ou, R. Liu and D. Ding, *Adv. Mater.*, 2020, **32**, 1806331.





- 108 C. Chen, X. Ni, H. Tian, Q. Liu, D. Guo and D. Ding, *Angew. Chem., Int. Ed.*, 2020, **59**, 10008–10012.
- 109 J. Dai, Y. Cheng, J. Wu, Q. Wang, W. Wang, J. Yang, Z. Zhao, X. Lou, F. Xia, S. Wang and B. Z. Tang, *ACS Nano*, 2020, **14**, 14698–14714.
- 110 F. Xia, J. Wu, X. Wu, Q. Hu, J. Dai and X. Lou, *Acc. Chem. Res.*, 2019, **52**, 3064–3074.
- 111 F. Wu, X. Wu, Z. Duan, Y. Huang, X. Lou and F. Xia, *Small*, 2019, **15**, 1804839.
- 112 J. Yang, J. Wei, F. Luo, J. Dai, J. J. Hu, X. Lou and F. Xia, *Top. Curr. Chem.*, 2020, **378**, 47.
- 113 Y. Cheng, C. Sun, R. Liu, J. Yang, J. Dai, T. Zhai, X. Lou and F. Xia, *Angew. Chem., Int. Ed.*, 2019, **58**, 5049–5053.
- 114 J. Yang, J. Dai, Q. Wang, Y. Cheng, J. Guo, Z. Zhao, Y. Hong, X. Lou and F. Xia, *Angew. Chem., Int. Ed.*, 2020, **59**, 20405–20410.
- 115 Z. Meng, Z. Kang, C. Sun, S. Yang, B. Zhao, S. Feng, Q. Meng and K. Liu, *Nanoscale*, 2018, **10**, 1215–1227.
- 116 N. Li, H. Yang, Z. Yu, Y. Li, W. Pan, H. Wang and B. Tang, *Chem. Sci.*, 2017, **8**, 2816–2822.
- 117 A. K. Oyelere, P. C. Chen, X. Huang, I. H. El-Sayed and M. A. El-Sayed, *Bioconjugate Chem.*, 2007, **18**, 1490–1497.
- 118 Y. Wang, J. Chen and J. Irudayaraj, *ACS Nano*, 2011, **5**, 9718–9725.
- 119 M. E. Muroski, J. M. Kogot and G. F. Strouse, *J. Am. Chem. Soc.*, 2012, **134**, 19722–19730.
- 120 L. Q. Chen, S. J. Xiao, P. P. Hu, L. Peng, J. Ma, L. F. Luo, Y. F. Li and C. Z. Huang, *Anal. Chem.*, 2012, **84**, 3099–3110.
- 121 N. L. Rosi, D. A. Giljohann, C. S. Thaxton, A. K. R. Lytton-Jean, M. S. Han and C. A. Mirkin, *Science*, 2006, **312**, 1027–1030.
- 122 M. E. Muroski, T. J. Morgan Jr, C. W. Levenson and G. F. Strouse, *J. Am. Chem. Soc.*, 2014, **136**, 14763–14771.
- 123 D. Wang, Y. Tong, Y. Li, Z. Tian, R. Cao and B. Yang, *Diamond Relat. Mater.*, 2013, **36**, 26–34.
- 124 A. Bumb, S. K. Sarkar, N. Billington, M. W. Brechbiel and K. C. Neuman, *J. Am. Chem. Soc.*, 2013, **135**, 7815–7818.
- 125 S. J. Yu, M. W. Kang, H. C. Chang, K. M. Chen and Y. C. Yu, *J. Am. Chem. Soc.*, 2005, **127**, 17604–17605.
- 126 H. M. Leung, M. S. Chan, L. S. Liu, S. W. Wong, T. W. Lo, C. H. Lau, C. Tin and P. K. Lo, *ACS Sustainable Chem. Eng.*, 2018, **6**, 9671–9681.
- 127 B. Kim, H. B. Pang, J. Kang, J. H. Park, E. Ruoslahti and M. J. Sailor, *Nat. Commun.*, 2018, **9**, 1969.
- 128 M. Dowaidar, H. N. Abdelhamid, M. Hällbrink, K. Freimann, K. Kurrikoff, X. Zou and Ü. Langel, *Sci. Rep.*, 2017, **7**, 9159.
- 129 A. Bolhassani, S. Javanzad, T. Saleh, M. Hashemi, M. R. Aghasadeghi and S. M. Sadat, *Hum. Vaccines Immunother.*, 2014, **10**, 321–332.
- 130 G. Im II, *J. Biomed. Mater. Res., Part A*, 2013, **101**, 3009–3018.
- 131 W. T. Godbey, K. K. Wu and A. G. Mikos, *J. Controlled Release*, 1999, **60**, 149–160.
- 132 G. Borchard, *Adv. Drug Delivery Rev.*, 2001, **52**, 145–150.
- 133 S. Roy, K. Zhang, T. Roth, S. Vinogradov, R. S. Kao and A. Kabanov, *Nat. Biotechnol.*, 1999, **17**, 476–479.
- 134 J. Dai, M. Xu, Q. Wang, J. Yang, J. Zhang, P. Cui, W. Wang, X. Lou, F. Xia and S. Wang, *Theranostics*, 2020, **10**, 2385–2398.
- 135 V. Toncheva, M. A. Wolfert, P. R. Dash, D. Oupicky, K. Ulbrich, L. W. Seymour and E. H. Schacht, *Biochim. Biophys. Acta*, 1998, **1380**, 354–368.
- 136 D. Cheng, X. Zhang, Y. Gao, L. Ji, D. Hou, Z. Wang, W. Xu, Z. Qiao and H. Wang, *J. Am. Chem. Soc.*, 2019, **141**, 7235–7239.
- 137 L. Liu, W. Qiu, Y. Zhang, B. Li, C. Zhang, F. Gao, L. Zhang and X. Zhang, *Adv. Funct. Mater.*, 2017, **27**, 1700220.
- 138 H. Hosseinkhani, F. Abedini, K. Ou and A. J. Domb, *Polym. Adv. Technol.*, 2015, **26**, 198–211.
- 139 H. X. Wang, Z. Song, Y. H. Lao, X. Xu, J. Gong, D. Cheng, S. Chakraborty, J. S. Park, M. Li, D. Huang, L. Yin, J. Cheng and K. W. Leong, *Proc. Natl. Acad. Sci. U. S. A.*, 2018, **115**, 4903–4908.
- 140 L. Kelland, *Nat. Rev. Cancer*, 2007, **7**, 573–584.
- 141 D. Wang and S. J. Lippard, *Nat. Rev. Drug Discovery*, 2005, **4**, 307–320.
- 142 S. Dhar, F. X. Gu, R. Langer, O. C. Farokhzad and S. J. Lippard, *Proc. Natl. Acad. Sci. U. S. A.*, 2008, **105**, 17356–17361.
- 143 S. He, C. Li, Q. i Zhang, J. Ding, X. J. Liang, X. Chen, H. Xiao, X. Chen, D. Zhou and Y. Huang, *ACS Nano*, 2018, **12**, 7272–7281.
- 144 J. M. Farrow, J. C. Yang and C. P. Evans, *Nat. Rev. Urol.*, 2014, **11**, 508–516.
- 145 Y. Lin, Y. Wang, H. An, B. Qi, J. Wang, L. Wang, J. Shi, L. Mei and H. Wang, *Nano Lett.*, 2019, **19**, 2968–2978.
- 146 S. Guan, A. Munder, S. Hedtfeld, P. Braubach, S. Glage, L. Zhang, S. Lienenklaus, A. Schultze, G. Hasenpusch, W. Garrels, F. Stanke, C. Miskey, S. M. Johler, Y. Kumar, B. Tümmler, C. Rudolph, Z. Ivics and J. Rosenecker, *Nat. Nanotechnol.*, 2019, **14**, 287–297.
- 147 Y. Sun, X. Ye, M. Cai, X. Liu, J. Xiao, C. Zhang, Y. Wang, L. Yang, J. Liu, S. Li, C. Kang, B. Zhang, Q. Zhang, Z. Wang, A. Hong and X. Wang, *ACS Nano*, 2016, **10**, 5759–5768.

