

# Energy & Environmental Science

Volume 15  
Number 12  
December 2022  
Pages 4853–5436

rsc.li/ees



ISSN 1754-5706

**PAPER**

Dong Ki Lee, Jeehye Byun *et al.*  
Solar-driven H<sub>2</sub>O<sub>2</sub> production *via* cooperative auto- and photocatalytic oxidation in fine-tuned reaction media

Cite this: *Energy Environ. Sci.*, 2022, 15, 5082

# Solar-driven H<sub>2</sub>O<sub>2</sub> production *via* cooperative auto- and photocatalytic oxidation in fine-tuned reaction media†

Byeong Cheul Moon, <sup>‡a</sup> Bolormaa Bayarkhuu, <sup>‡bc</sup> Kai A. I. Zhang, <sup>d</sup> Dong Ki Lee <sup>\*acef</sup> and Jeehye Byun <sup>\*bc</sup>

Solar photocatalysis has emerged as a sustainable route to produce H<sub>2</sub>O<sub>2</sub>; however, the structural design of photocatalysts makes them expensive, limiting their practical applications. Inspired by the industrial anthraquinone process, we developed a new reaction design for solar H<sub>2</sub>O<sub>2</sub> production using an organic working solution (OWS) comprising aryl alcohols and a metal-free polymeric photocatalyst. The synergistic auto- and photocatalytic oxidation of aryl alcohols in the OWS allowed for the quantitative generation of H<sub>2</sub>O<sub>2</sub> by counter O<sub>2</sub> reduction. The fine modulation of the OWS with water enhanced the photocatalytic route, resulting in an unprecedented H<sub>2</sub>O<sub>2</sub> production rate of 46.9 mmol h<sup>-1</sup> g<sup>-1</sup> with a solar-to-chemical conversion efficiency of 1.1% under simulated sunlight. Pure H<sub>2</sub>O<sub>2</sub> was obtained after extraction and purification by membrane filtration, and was directly used in large-scale water purification as a proof of concept. This study demonstrates the importance of reaction design in photocatalytic applications and will promote future advancements in green, solar-driven H<sub>2</sub>O<sub>2</sub> production.

Received 5th August 2022,  
Accepted 31st October 2022

DOI: 10.1039/d2ee02504c

rsc.li/ees

## Broader context

The industrial synthesis of H<sub>2</sub>O<sub>2</sub> is based on the anthraquinone auto-oxidation process, which requires high-energy consumption and an expensive metal catalyst. Solar photocatalysis has been suggested as a green and sustainable process to produce H<sub>2</sub>O<sub>2</sub>. Although there have been significant advances in materials design to improve the H<sub>2</sub>O<sub>2</sub> production efficiency, the photocatalytic H<sub>2</sub>O<sub>2</sub> production performance remains insufficient to meet industrial demands. In this study, we design a new reaction environment using aryl alcohol as an organic photo-oxidation substrate. With a metal-free covalent triazine framework (CTF) as a model photocatalyst, we combine photo-oxidation with O<sub>2</sub> reduction under fully organic conditions for the co-production of H<sub>2</sub>O<sub>2</sub> and aryl aldehyde. Furthermore, this organic system allows for the light-activated autocatalytic oxidation of aryl alcohol, facilitating O<sub>2</sub> reduction kinetics by photo-initiated radicals. Inspired by the organic working solution of the anthraquinone process, we fine-tune the reaction composition by varying the water-aryl alcohol-solvent ratios to improve the photocatalytic pathway, achieving one of the highest solar-to-chemical conversion efficiencies ever reported. This study demonstrates that tailoring the reaction media is a simple but effective route for promoting overall solar H<sub>2</sub>O<sub>2</sub> productivity, providing a new opportunity in photocatalytic reactions.

## Introduction

Solar photocatalysis provides a green route for the synthesis of hydrogen peroxide (H<sub>2</sub>O<sub>2</sub>) from O<sub>2</sub> and sunlight.<sup>1</sup> Among the different reported classes of photocatalysts, metal-free polymeric photocatalysts have attracted considerable attention because their structures and properties are amenable to modification,<sup>2,3</sup> thus allowing significant improvement in the photocatalytic H<sub>2</sub>O<sub>2</sub> production efficiencies. Compared to metallic semiconductors, polymeric photocatalysts enable the stable generation of H<sub>2</sub>O<sub>2</sub>, inhibiting undesirable H<sub>2</sub>O<sub>2</sub> decomposition on the catalytic surfaces.<sup>4,5</sup> Recent state-of-the-art examples of methods to prepare polymeric photocatalysts

<sup>a</sup> Clean Energy Research Center, Korea Institute of Science and Technology, Seoul 02792, Republic of Korea. E-mail: dnklee@kist.re.kr

<sup>b</sup> Water Cycle Research Center, Korea Institute of Science and Technology, Seoul 02792, Republic of Korea. E-mail: jbyun@kist.re.kr

<sup>c</sup> Division of Energy and Environment Technology, KIST-School, University of Science and Technology, Seoul 02792, Republic of Korea

<sup>d</sup> Department of Materials Science, Fudan University, Shanghai 200433, P. R. China

<sup>e</sup> Graduate School of Energy and Environment, Korea University, Seoul 02841, Republic of Korea

<sup>f</sup> Department of Chemical and Biomolecular Engineering, Yonsei-KIST Convergence Research Institute, Yonsei University, Seoul 03722, Republic of Korea


† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2ee02504c>

‡ These authors contributed equally.







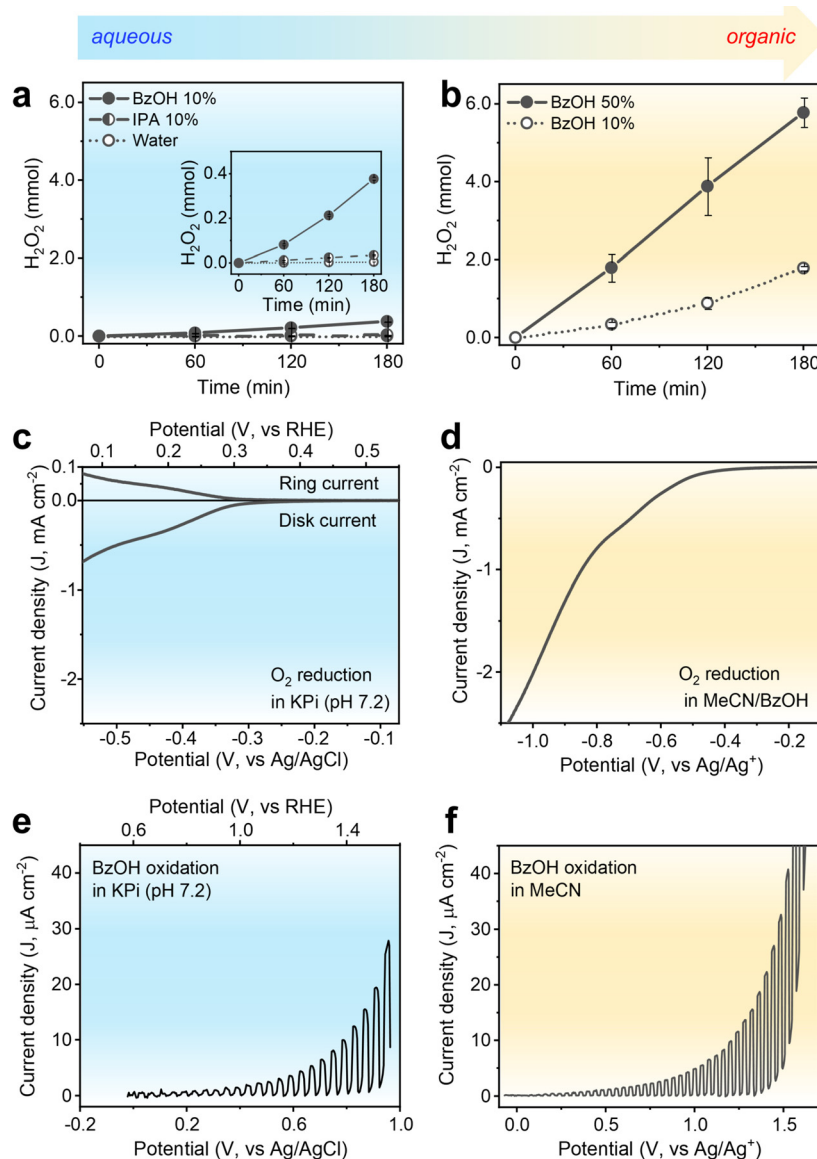

**Fig. 2** (a) Time-dependent photocatalytic  $\text{H}_2\text{O}_2$  production using CTF-Ph under aqueous conditions. Reaction conditions:  $\text{O}_2$ -saturated water (27 mL), 10% hole scavenger (3 mL; benzyl alcohol (BzOH) or isopropanol (IPA)), photocatalyst (50 mg), AM 1.5G simulated sunlight ( $\sim 980 \text{ W m}^{-2}$ ), 298 K. (b) Photocatalytic  $\text{H}_2\text{O}_2$  production under organic conditions. Reaction conditions: BzOH (3 mL for 10% or 15 mL for 50%),  $\text{O}_2$ -saturated acetonitrile (MeCN) (27 mL or 15 mL), photocatalyst (50 mg), simulated sunlight, 298 K. (c) Rotating ring-disk electrode (RRDE) voltammogram of  $\text{O}_2$ -saturated 0.1 M BzOH in 0.1 M phosphate buffer (KPi, pH 7.2). The applied potential on the Pt ring electrode was 1.0 V vs. Ag/AgCl. (d) RRDE voltammogram of  $\text{O}_2$ -saturated 0.1 M BzOH in MeCN-0.1 M tetrabutylammonium hexafluorophosphate (TBAPF<sub>6</sub>). Photoelectrochemical oxidation of 0.1 M BzOH using the CTF-Ph photoelectrode in (e) aqueous 0.1 M KPi and (f) 0.1 M TBAPF<sub>6</sub>-MeCN under simulated sunlight. All the LSV scans were performed at a scan rate of  $10 \text{ mV s}^{-1}$ , and the rotating speed of the RDE was 1600 rpm.

consistent with the results obtained using a previously reported CTF photocatalyst.<sup>27</sup> When the reaction was conducted in an Ar-saturated atmosphere, a trace amount of  $\text{H}_2\text{O}_2$  was obtained, indicating that  $\text{H}_2\text{O}_2$  was primarily generated by the two-electron  $\text{O}_2$  reduction (Fig. S6, ESI<sup>†</sup>). The  $\text{H}_2\text{O}_2$  production efficiency was further enhanced by the quantitative addition of hole scavengers to water. When the typical hole scavenger isopropanol (IPA) was used in combination with CTF-Ph, a higher amount of  $\text{H}_2\text{O}_2$  was produced ( $34.3 \mu\text{mol}$ ). When BzOH was used as a hole scavenger, the amount of  $\text{H}_2\text{O}_2$  produced

significantly increased to  $377.2 \mu\text{mol}$  after 3 h of solar irradiation. CTF-Ph is known as a low-performing photocatalyst owing to its large energy band gap;<sup>28</sup> hence, the drastic increase in  $\text{H}_2\text{O}_2$  production after the addition of BzOH is unexpected. Moreover, the current density–voltage plot of CTF-Ph exhibited a high anodic peak current for BzOH oxidation (Fig. S7, ESI<sup>†</sup>), indicating that BzOH plays a crucial role as a hole scavenger.

The BzOH-rich environment was thus achieved under organic conditions with acetonitrile (MeCN) as the solvent. As shown in Fig. 2b,  $\text{H}_2\text{O}_2$  production under organic conditions



is one order of magnitude higher than that under aqueous conditions. The reaction in the presence of CTF-Ph and 10 vol% of BzOH produced 1.79 mmol of H<sub>2</sub>O<sub>2</sub> under light irradiation for 3 h. A higher loading of BzOH (up to 50 vol%) increased the H<sub>2</sub>O<sub>2</sub> production up to 5.78 mmol, and thereafter, the BzOH loading was maintained at 50 vol% in further experiments. Other aryl alcohol substrates, such as substituted BzOHs and secondary aryl alcohols, can also be used as hole scavengers in photocatalytic H<sub>2</sub>O<sub>2</sub> production (Fig. S8, ESI†).

To understand the origin of the discrepancy between the performances obtained under aqueous and organic conditions, electrochemical evaluation of CTF-Ph was conducted. The electrochemical O<sub>2</sub> reduction was analyzed *via* rotating ring-disk electrode (RRDE) measurements. The linear voltammetry sweep (LSV) curve of CTF (Fig. 2c) in an aqueous potassium phosphate buffer (KPi, pH 7.2) showed that the onset potential for the O<sub>2</sub> reduction current was approximately  $-0.2$  V *vs.* Ag/AgCl and the calculated H<sub>2</sub>O<sub>2</sub> selectivity was  $\sim 60\%$  (Fig. S9, ESI†). In contrast, the LSV curve of CTF-Ph in the BzOH–MeCN solution showed a substantial increase in the O<sub>2</sub> reduction current (Fig. 2d) compared to that under aqueous conditions. This demonstrates that the O<sub>2</sub> reduction activity of CTF can be significantly enhanced by replacing an aqueous electrolyte with an organic one.

The photoelectrochemical oxidation properties of CTF-Ph, which is the other half of the photoredox system, were examined. The LSV curve under aqueous conditions indicates a clear photo-response for water oxidation with an onset potential shift of  $\sim 0.7$  V (from 0.9 to 0.2 V *vs.* Ag/AgCl) (Fig. S10, ESI†). When 0.1 M BzOH was added to the aqueous electrolyte, CTF-Ph demonstrated a cathodic shift in the onset of the photocurrent (Fig. 2e). This is because the major oxidation reaction changed from water oxidation to BzOH oxidation. The photovoltage of CTF also slightly increased from 0.7 to 1.0 V in the presence of BzOH. The addition of IPA to water, on the other hand, resulted in a minor increase in photocurrent as a less efficient hole scavenger (Fig. S10, ESI†). With the BzOH-rich environment in MeCN, the CTF-Ph photoelectrode exhibited an additional enhancement in both the photovoltage (from 1.0 to 1.5 V) and photocurrent for BzOH oxidation compared to those in the aqueous electrolyte (Fig. 2f). This indicates that BzOH oxidation is thermodynamically and kinetically more facile than water and IPA oxidation, thus enhancing the O<sub>2</sub> reduction activity of the CTF by improving the photogenerated charge separation.

Electrochemical assessments indicated that the O<sub>2</sub> reduction and BzOH oxidation activities of CTF-Ph were affected by the solution composition. Nonetheless, the intrinsic activity of CTF in different media does not fully account for the enhanced H<sub>2</sub>O<sub>2</sub> production under organic conditions. The potential auto-oxidation of BzOH in the UV region is an important aspect to investigate. The control experiment showed that a quantitative amount of H<sub>2</sub>O<sub>2</sub> was produced under simulated sunlight illumination even without the addition of CTF-Ph (Fig. S11, ESI†). BzCHO was generated in almost the same amount as H<sub>2</sub>O<sub>2</sub>, implying that their production is interrelated. Notably, these

two products were not detected when the organic solution was irradiated with visible light ( $>400$  nm), demonstrating that the UV-initiated autocatalytic reaction under organic conditions significantly contributed to the generation of H<sub>2</sub>O<sub>2</sub> and BzCHO.

### Solar-driven H<sub>2</sub>O<sub>2</sub> production in the designed OWSs

Since organic conditions enhanced the solar H<sub>2</sub>O<sub>2</sub> production, several OWSs were designed by using different molar ratios of water to BzOH (0, 10, 50, 66, and 98.5 mol%) (Table S1, ESI†). The effect of water on the photocatalytic activity of the CTF and the autocatalytic contribution was determined by measuring the amounts of H<sub>2</sub>O<sub>2</sub> and BzCHO produced. Significant amounts of H<sub>2</sub>O<sub>2</sub> and BzCHO were produced without a photocatalyst (denoted as “BLK”), with the maximum amounts of H<sub>2</sub>O<sub>2</sub> and BzCHO (4.90 and 6.17 mmol, respectively) produced under water-free conditions. The performance with BLK rapidly decreased with the addition of water. However, in the presence of CTF-Ph, the overall production of H<sub>2</sub>O<sub>2</sub> and BzCHO was higher than that obtained under BLK conditions. Furthermore, the photocatalytic efficiency of the CTF increased with the addition of small amounts of water to the OWS. For instance, CTF-Ph demonstrated the maximum H<sub>2</sub>O<sub>2</sub> and BzCHO production (7.04 and 7.44 mmol, respectively) in the OWS for 3 h with a 10 mol% addition of water (Fig. 3a and b); however, a small amount of benzyl benzoate (BBA, 0.11 mmol) was generated as a side product<sup>29</sup> (Fig. S12, ESI†). The formation of H<sub>2</sub> gas by a competing reaction of proton reduction was marginal in the OWS even with the excess water (Fig. S13, ESI†). To the best of our knowledge, our method of solar-driven H<sub>2</sub>O<sub>2</sub> production using an OWS and CTF-Ph resulted in one of the highest recorded solar-to-chemical conversion (SCC) efficiencies of up to 1.1% with a H<sub>2</sub>O<sub>2</sub> production rate of 46.9 mmol h<sup>-1</sup> g<sup>-1</sup>, comparable with the most efficient water splitting photocatalyst (Fig. 3c and Table S2 for a full comparison, ESI†).<sup>5,7,30,31</sup>

Despite the significant contribution of autocatalytic oxidation toward H<sub>2</sub>O<sub>2</sub> production under solar irradiation, the photocatalytic effect remained evident. For instance, P25 TiO<sub>2</sub> as a control photocatalyst with a strong oxidation potential (2.69 V *vs.* Ag/Ag<sup>+</sup>, Fig. S1, ESI†) exhibited far lower production efficiencies, generating a maximum of 1.97 and 3.13 mmol of H<sub>2</sub>O<sub>2</sub> and BzCHO, respectively, with a 50 mol% addition of water (Fig. 3a and b). The photocatalytic contribution was determined by subtracting the amounts of H<sub>2</sub>O<sub>2</sub> and BzCHO produced using BLK from those obtained when the photocatalyst was used (Photocat. – BLK in Fig. 3a and b). When TiO<sub>2</sub> was used, an adverse effect on H<sub>2</sub>O<sub>2</sub> and BzCHO production was observed, indicating that the reaction was governed by the type of photocatalyst used (Fig. S14, ESI†). Because of this dependence, sequentially changing the photocatalyst in the reaction at each stage changed the reaction performance (Fig. 3d). TiO<sub>2</sub> has insufficient potential for O<sub>2</sub> reduction (Fig. S1, ESI†) and is likely to decompose H<sub>2</sub>O<sub>2</sub> under both aqueous and organic conditions (Fig. S15 and S16, ESI†). This suggests that metal-free photocatalysts, such as common polymeric photocatalysts, are more suitable for these reactions (Fig. S17, ESI†).



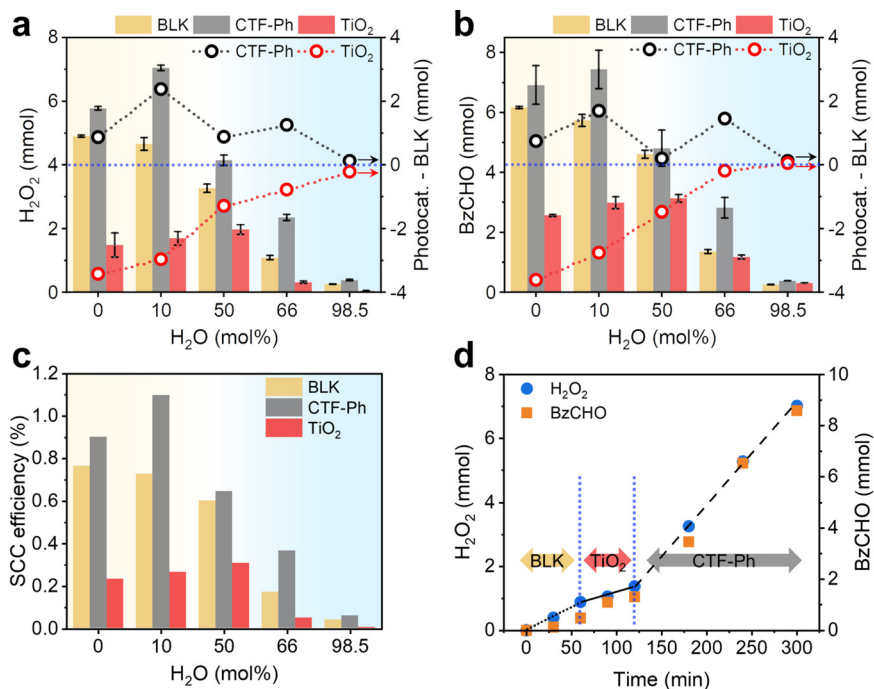


Fig. 3 Reaction design with varying molar ratios of water to BzOH in MeCN. Solar-driven production of (a) H<sub>2</sub>O<sub>2</sub> and (b) benzaldehyde (BzCHO) in the organic working solution (OWS) with and without the photocatalyst (BLK). The photocatalytic effect was estimated by subtracting the amount of products obtained under BLK conditions from those obtained using the photocatalysts (Photocat.-BLK). (c) Solar-to-chemical conversion (SCC) efficiencies of H<sub>2</sub>O<sub>2</sub> production under AM 1.5G simulated sunlight irradiation for 3 h. (d) Sequential shift of photocatalysts in the OWS. Reaction conditions: photocatalyst (50 mg), organic solution (30 mL; 50% BzOH, 50% MeCN, 10 mol% H<sub>2</sub>O), simulated sunlight ( $\sim 980 \text{ W m}^{-2}$ ), O<sub>2</sub> (1 bar), 298 K. In the shift, the photocatalyst was filtered through a 0.22  $\mu\text{m}$  hydrophilic PTFE syringe filter and O<sub>2</sub> was purged in the reaction solution.

### Mechanism of solar-driven H<sub>2</sub>O<sub>2</sub> production *via* interplay between auto- and photo-catalysis

To reveal the reaction mechanism in the OWS, the radical intermediate was monitored by EPR measurements under simulated sunlight irradiation. The selective O<sub>2</sub> reduction on CTF-Ph was evidenced by the 5,5-dimethyl-1-pyrroline N-oxide (DMPO)-hydroperoxyl ( $\bullet\text{OOH}$ ) adduct ( $g = 2.00561$ ;  $A_{\text{N}} = 13.5 \text{ G}$ ;  $A_{\text{H},\beta} = 11.0 \text{ G}$ ;  $A_{\text{H},\gamma} = 1.30 \text{ G}$ ) (Fig. 4a).<sup>32,33</sup> In 100% BzOH in air, a clear sextet spectrum was obtained by CTF-Ph, which is attributed to a DMPO-benzyl (OR $\bullet$ ) adduct ( $g = 2.00561$ ;  $A_{\text{N}} = 15.3 \text{ G}$ ;  $A_{\text{H}} = 22.2 \text{ G}$ ) (Fig. 4b),<sup>32,33</sup> indicating that BzOH oxidation mainly proceeds *via* an  $\alpha$ -hydroxybenzyl radical intermediate.<sup>24,34</sup> Both DMPO- $\bullet\text{OOH}$  and DMPO-OR $\bullet$  adducts were also observed in BLK, implying that autocatalysis takes place by free radical reactions.


*In situ* EPR profiles further provided evidence of the progress of the photo- and auto-catalytic reactions. In the photocatalytic reaction with water (CTF-Ph + H<sub>2</sub>O), the strong quartet signals of the DMPO- $\bullet\text{OOH}$  adduct were mainly observed at an early stage (Fig. 4c and Fig. S18, ESI $^\dagger$ ). The signal intensity reached a maximum within a few minutes and began to decrease with O<sub>2</sub> consumption. The bottom projection showed the evolution of the DMPO-OR $\bullet$  adduct at 334 and 339 mT after approximately 10 min. In contrast, in the autocatalytic reaction with water (BLK + H<sub>2</sub>O), the intensity of the DMPO- $\bullet\text{OOH}$  adduct signals was significantly lower and quickly decayed (Fig. 4d). Instead, a strong peak from the DMPO-OR $\bullet$  adduct was observed on the

projection in BLK + H<sub>2</sub>O. Time-resolved quantitative analysis showed that the photogenerated radical signal was more intense and long-lived in CTF-Ph + H<sub>2</sub>O compared to that in BLK + H<sub>2</sub>O (Fig. 4e). Although a higher level of radical formation was also apparent with CTF-Ph compared to that with BLK in the absence of water (Fig. S19, ESI $^\dagger$ ), the addition of water further enhanced the radical generation. This observation was consistent with the improved H<sub>2</sub>O<sub>2</sub> production in the water-containing OWS with CTF-Ph.

First, in BLK as autocatalysis, the formation of hydroperoxyl and  $\alpha$ -hydroxybenzyl radicals was substantially lower than that in the presence of CTF-Ph (Fig. 4a and b). Direct activation of BzOH under UV irradiation is known to form an alcohol radical cation and subsequently an alkoxy radical,<sup>23</sup> however, this was not mainly observed under solar irradiation. As shown in Fig. S11 (ESI $^\dagger$ ), the autocatalytic reaction generates H<sub>2</sub>O<sub>2</sub> under irradiation with UV-A light (315–400 nm), which is consistent with the light absorption range of the BzCHO solution (Fig. S20, ESI $^\dagger$ ). Even in pure BzOH, a minor amount of BzCHO exists at a concentration of 1414.5 ppm (Fig. S21a, ESI $^\dagger$ ). Under solar irradiation, BzCHO is excited to the  $^1\text{n},\pi^*$  state by absorbing light longer than 300 nm, and the singlet state of BzCHO is then transformed to the  $^3\text{n},\pi^*$  state by intersystem crossing.<sup>35</sup> The excited triplet state of BzCHO can abstract hydrogen from BzOH to generate an  $\alpha$ -hydroxybenzyl radical that is responsible for O<sub>2</sub> activation.<sup>36</sup> The addition of water under the BLK conditions led to a rapid decrease in production efficiency,





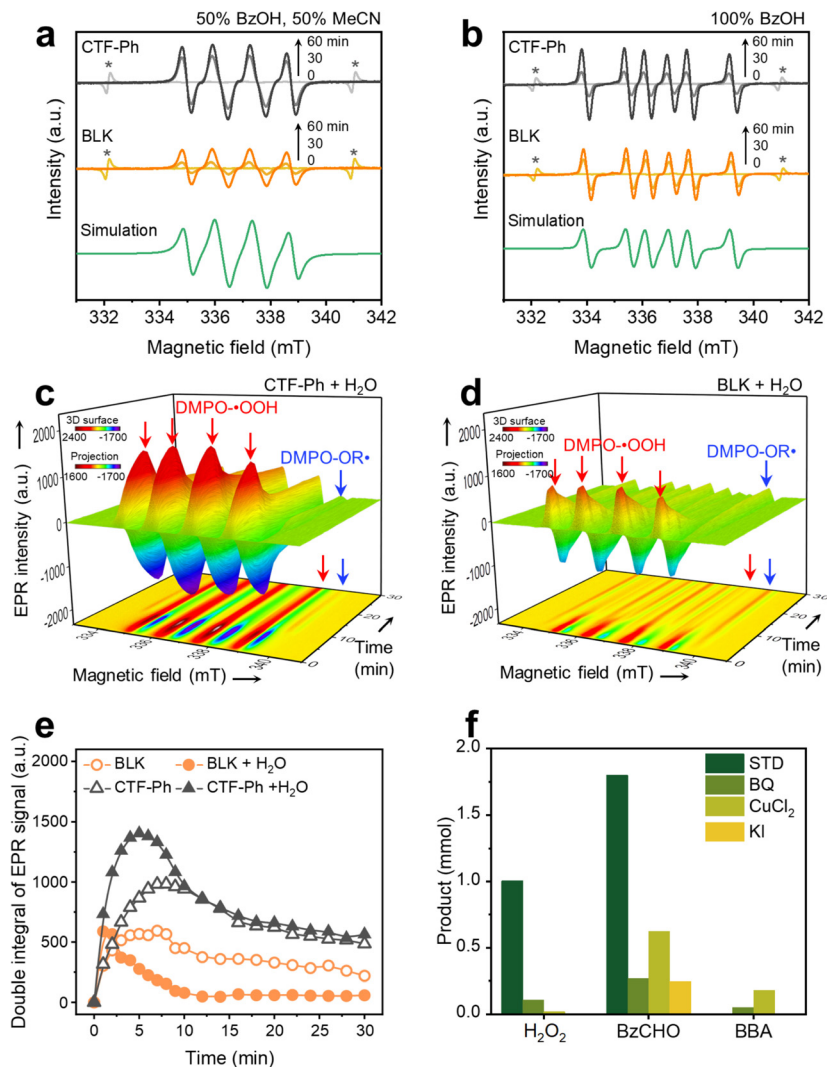

**Fig. 4** Electron paramagnetic resonance (EPR) spectra of (a) DMPO-hydroperoxyl ( $\cdot\text{OOH}$ ) and (b) DMPO-benzyl ( $\text{OR}\cdot$ ) radical with CTF-Ph and without the photocatalyst (BLK) under simulated sunlight irradiation ( $\sim 980 \text{ W m}^{-2}$ ). Reaction conditions: (a) BzOH (1.5 mL), MeCN (1.5 mL),  $\text{O}_2$  (purged for 30 min), 298 K, DMPO (20  $\mu\text{L}$ ); (b) BzOH (3 mL), air (exposed to air for 3 h), 298 K, DMPO (20  $\mu\text{L}$ ). EPR spectra were obtained at 0, 30, and 60 min of irradiation. With the photocatalyst, CTF-Ph (10 mg) was added in the reaction vessel (4 mL vial). The asterisk indicates a signal from the Mn marker used for calibration. Time-dependent *in situ* EPR spectra of (c) CTF-Ph and (d) BLK in an  $\text{O}_2$ -saturated OWS (50% BzOH, 50% MeCN, 5 mol%  $\text{H}_2\text{O}$ ). (e) Double integral of the *in situ* EPR signals for CTF-Ph and BLK in the absence and presence of water (5 mol%) in the OWS. (f) Photocatalytic performance of CTF-Ph in the OWS with addition of radical scavengers. Copper chloride ( $\text{CuCl}_2$ ), potassium iodide (KI), and 1,4-benzoquinone (BQ) were tested as photogenerated electron ( $e^-$ ), photoinduced hole ( $h^+$ ), and hydroperoxyl radical ( $\text{O}_2^{\cdot-}$ ) scavengers, respectively. Reaction conditions: CTF-Ph (20 mg), scavenger (166.7  $\mu\text{mol}$ ), organic solution (10 mL; 50% BzOH, 50% MeCN), simulated sunlight,  $\text{O}_2$  (1 bar), 298 K.

which could be ascribed to the rate-retarding effect of water in the hydrogen abstraction reaction.<sup>37,38</sup>

Intentionally spiking the BLK solution with a minimal amount of BzCHO, however, did not always increase the  $\text{H}_2\text{O}_2$  production after solar irradiation (Fig. S21b–d, ESI<sup>†</sup>). By increasing the BzCHO content in BzOH, the formation of the side product BBA could rather increase. Notably, benzoic acid as an over-oxidized product was not detected under both BLK and CTF-Ph conditions, indicating that BBA did not result from the esterification of BzOH with benzoic acid. With a higher initial BzCHO concentration, a larger amount of benzoyl radicals can be produced by the decomposition of the excited triplet state of BzCHO.<sup>36</sup> On the other hand, the photocatalytic

oxidation of BzOH generated an alkoxy radical under visible light as a minor intermediate (Fig. S22, ESI<sup>†</sup>). The coupling between the benzoyl radical and alkoxy radical led to the production of a larger amount of BBA side product. A catalytic amount of BzCHO in pure BzOH was thereby sufficient to attain the autocatalytic pathway without forming the excessive side product. Nevertheless, the amount of BzCHO can vary depending on the scale of the OWS, which should be a key consideration when scaling up the reaction in future studies.


Along with autocatalysis, the photocatalytic role of CTF-Ph in the OWS was further investigated. Control experiments with radical scavengers proved the importance of photogenerated electrons and holes in the  $\text{O}_2$  reduction and alcohol oxidation



processes (Fig. 4f). The  $\text{H}_2\text{O}_2$  and BzCHO production efficiencies of CTF-Ph were both affected by the addition of electron and hole scavengers compared to those in the standard reaction (STD). In particular, the BzCHO production significantly decreased by the addition of a  $\text{h}^+$  scavenger. The quenching of the  $\text{O}_2^{\bullet-}$  radical also decreased the BzCHO production of CTF-Ph, indicating that the oxidation of the BzOH radical intermediate by the  $\text{O}_2^{\bullet-}$  radical is a critical pathway for BzCHO formation. Although the formation of the BBA side product was insignificant in STD, it was somewhat facilitated when the  $\text{O}_2$  reduction was suppressed by scavenging photoinduced electrons and  $\text{O}_2^{\bullet-}$ . Therefore, the selective formation of  $\text{H}_2\text{O}_2$  and BzCHO only occurs through cooperative  $\text{O}_2$  reduction and BzOH oxidation reactions.

The positive effect of water in the respective  $\text{O}_2$  reduction and BzOH oxidation reactions with CTF-Ph was electrochemically evaluated using  $\text{H}_2\text{O}$ -MeCN mixtures (Table S3, ESI†). Notably, the amount of BzOH in the electrochemical studies was adjusted to be relatively smaller than that under the photocatalytic reaction conditions to circumvent inaccurate

readings of the reaction currents on the electrodes as a result of the limited water miscibility of BzOH and possible surface-impeding effects. When the water content was in the range of 0–50 vol%, the current density of BzOH oxidation was in the range of 0.9–1.4  $\text{mA cm}^{-2}$ , which then decreased to 0.7  $\text{mA cm}^{-2}$  when the water content was 60–100 vol% (Fig. 5a). Moreover, the  $\text{O}_2$  reduction current was significantly affected by the addition of a small amount of water to the electrolyte. An approximately 15-fold increase in the  $\text{O}_2$  reduction current was observed when the water content in the electrolyte increased from 0 to 10 vol%, followed by a rapid decrease in the current density when the water content was further increased from 50 to 100 vol%, indicating a volcano-like trend. The onset potentials for the  $\text{O}_2$  reduction and alcohol oxidation reactions shifted rapidly with the addition of water and became saturated at a water content of 10 vol% (Fig. 5b). The shifting direction was beneficial for both reactions: a cathodic shift for BzOH oxidation and an anodic shift for  $\text{O}_2$  reduction. The onset potential differences between the two opposite reactions ( $\Delta V_{\text{onset}}$ ) show that the addition of water up to 10 vol%

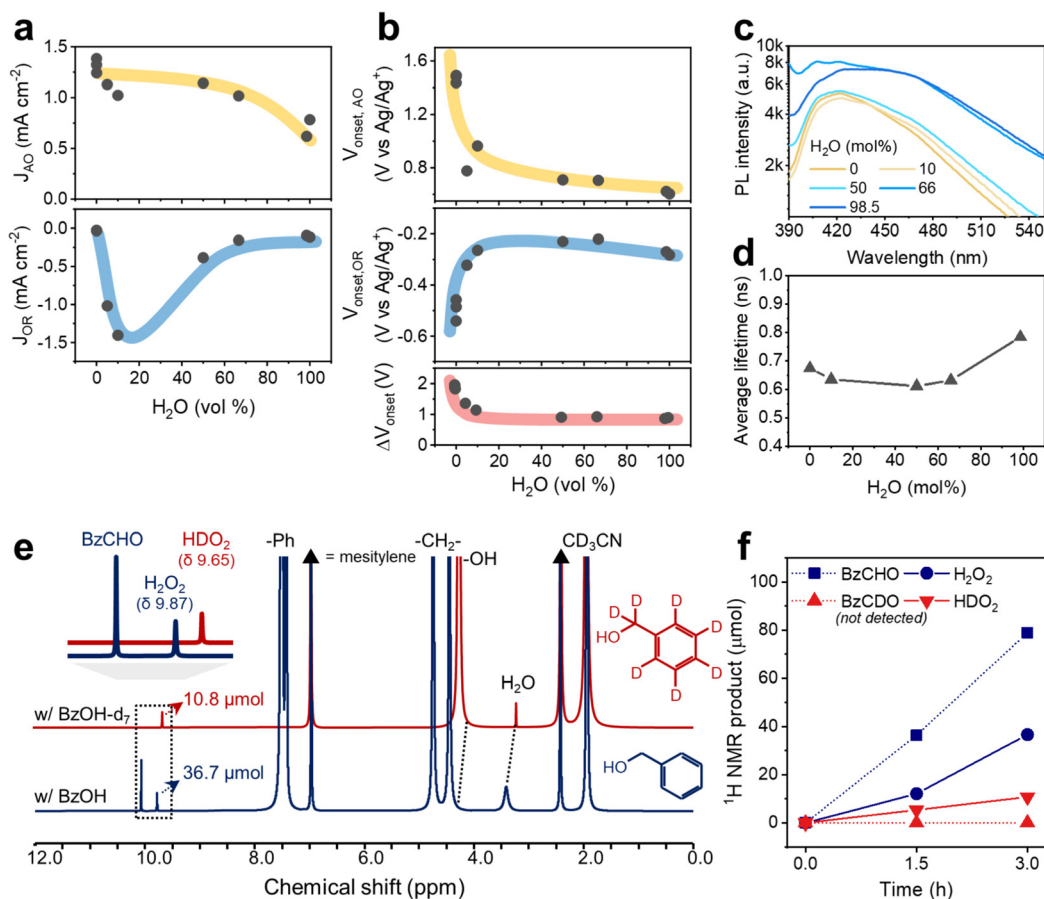

**Fig. 5** (a) Reaction currents and (b) onset voltage changes of CTF-Ph for  $\text{O}_2$  reduction (OR) and alcohol oxidation (AO) with different water contents in the  $\text{H}_2\text{O}$ -MeCN mixture with 0.1 M BzOH. The reaction current for  $\text{O}_2$  reduction and BzOH oxidation was determined to be  $-1.5$  V and  $+2.0$  V vs.  $\text{Ag}/\text{Ag}^+$ , respectively, and the onset potentials for both reactions were determined at the voltages when the absolute reaction current reaches  $10 \mu\text{A cm}^{-2}$ . 0.1 M  $\text{LiClO}_4$  was used as the supporting electrolyte. (c) Photoluminescence spectra and (d) average lifetimes of CTF-Ph dispersed in the OWS under  $\text{O}_2$ -saturated conditions. (e)  $^1\text{H}$  NMR isotope experiment using BzOH- $\text{d}_7$  and BzOH under  $\text{O}_2$ -saturated conditions for 3 h ( $\text{CD}_3\text{CN}$ , 298 K), and (f) the corresponding products quantified from the spectra using mesitylene as the internal standard. Reaction conditions: BzOH(- $\text{d}_7$ ) (1.5 mL), CTF-Ph photocatalyst (15 mg),  $\text{H}_2\text{O}$  (26  $\mu\text{L}$ ),  $\text{CD}_3\text{CN}$  (1.5 mL),  $\text{O}_2$  (1 bar), simulated sunlight ( $\sim 990 \text{ W m}^{-2}$ ), 298 K.









degradation profile of methylene blue (MB) in a mixture of purified H<sub>2</sub>O<sub>2</sub> and Fe(II) solution. The MB molecules rapidly degraded in only 10 s, demonstrating enhanced removal kinetics compared to the photolysis of MB under UV-A or normal H<sub>2</sub>O<sub>2</sub> treatment. Despite the industrial production of H<sub>2</sub>O<sub>2</sub> at high concentrations (27.5–70%), dilute H<sub>2</sub>O<sub>2</sub> solutions are required for on-site applications such as advanced oxidation processes in wastewater treatment (10–100 ppm).<sup>46</sup> Solar H<sub>2</sub>O<sub>2</sub> production in the OWS can meet this requirement by producing dilute H<sub>2</sub>O<sub>2</sub> solutions with high purity, thereby providing a practical alternative for decentralized H<sub>2</sub>O<sub>2</sub> production (Fig. 7d).<sup>47</sup>

## Conclusions

This study demonstrates a new reaction design of an organic working solution that can promote the solar production process of H<sub>2</sub>O<sub>2</sub> using a model polymeric photocatalyst. The organic working solution afforded the successful integration of alcohol oxidation with O<sub>2</sub> reduction for electron donor-free photocatalysis. Furthermore, the use of the organic solution resulted in the discovery of autocatalytic alcohol oxidation by photoexcitation of benzaldehyde impurity existing in fresh benzyl alcohol, significantly enhancing both H<sub>2</sub>O<sub>2</sub> and benzaldehyde production. The photocatalytic pathway was improved by fine-engineering the reaction composition using water, demonstrating that tailoring the reaction media is a simple but effective route for promoting overall H<sub>2</sub>O<sub>2</sub> productivity. Future work is suggested to improve the performance of the organic working solution by exploring autocatalytic organic molecule candidates. Photoexcitation of aromatic ketones would hold a key to enhancing solar-to-chemical conversion efficiency further. In addition to autocatalysis, structural controls on polymeric photocatalysts are required for selective O<sub>2</sub> reduction and extended light absorbance, but in a cost-effective manner. Finally, a system design that combines a scaled solar reactor with a membrane purification setup is needed. We believe that this study provides a breakthrough in photocatalytic reactions, bringing solar photocatalysis a step closer to industrial standards.

## Author contributions

D. K. L. and J. B. conceived and designed the project; B. C. M. and B. B. performed the experiments; B. C. M., D. K. L., and J. B. analyzed the data; K. A. I. Z., D. K. L., and J. B. discussed the results; D. K. L. and J. B. wrote the manuscript with contributions from all authors.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by a National Research Foundation of Korea (NRF) grant funded by the Korean government (MSIT)

(No. 2021R1C1C1005774 to J. B.; No. 2020M3H4A1A02084590 and No. 2022M3A9F3082336 to D. K. L.). The authors acknowledge support from the National Research Council of Science and Technology (NST) grant (CPS21051-100) and institutional programs of KIST (2E31932 to J. B. and 2E31831 to D. K. L.). The authors sincerely thank Dr Chanhee Boo (KIST) for the reverse osmosis membrane filtration experiments, Dr Yeongran Hong (KIST) for the <sup>1</sup>H NMR spectroscopy studies, and Sukyoun Son (KIST) for the GC-MS analysis.

## References

- 1 Y. Sun, L. Han and P. Strasser, *Chem. Soc. Rev.*, 2020, **49**, 6605–6631.
- 2 J. Lee, O. Buyukcakir, T.-W. Kwon and A. Coskun, *J. Am. Chem. Soc.*, 2018, **140**, 10937–10940.
- 3 Y. Wang, A. Vogel, M. Sachs, R. S. Sprick, L. Wilbraham, S. J. A. Moniz, R. Godin, M. A. Zwijnenburg, J. R. Durrant, A. I. Cooper and J. Tang, *Nat. Energy*, 2019, **4**, 746–760.
- 4 J. H. Lee, H. Cho, S. O. Park, J. M. Hwang, Y. Hong, P. Sharma, W. C. Jeon, Y. Cho, C. Yang, S. K. Kwak, H. R. Moon and J.-W. Jang, *Appl. Catal., B*, 2021, **284**, 119690.
- 5 Y. Shiraishi, T. Takii, T. Hagi, S. Mori, Y. Kofuji, Y. Kitagawa, S. Tanaka, S. Ichikawa and T. Hirai, *Nat. Mater.*, 2019, **18**, 985–993.
- 6 S. Wang, B. Cai and H. Tian, *Angew. Chem., Int. Ed.*, 2022, **61**, e202202733.
- 7 Z. Teng, Q. Zhang, H. Yang, K. Kato, W. Yang, Y.-R. Lu, S. Liu, C. Wang, A. Yamakata, C. Su, B. Liu and T. Ohno, *Nat. Catal.*, 2021, **4**, 374–384.
- 8 T. Sun, S. Zhao, W. Chen, D. Zhai, J. Dong, Y. Wang, S. Zhang, A. Han, L. Gu, R. Yu, X. Wen, H. Ren, L. Xu, C. Chen, Q. Peng, D. Wang and Y. Li, *Proc. Natl. Acad. Sci. U. S. A.*, 2018, **115**, 12692–12697.
- 9 P. Zhang, Y. Tong, Y. Liu, J. J. M. Vequizo, H. Sun, C. Yang, A. Yamakata, F. Fan, W. Lin, X. Wang and W. Choi, *Angew. Chem., Int. Ed.*, 2020, **59**, 16209–16217.
- 10 Y. Zhao, P. Zhang, Z. Yang, L. Li, J. Gao, S. Chen, T. Xie, C. Diao, S. Xi, B. Xiao, C. Hu and W. Choi, *Nat. Commun.*, 2021, **12**, 3701.
- 11 Z.-A. Lan, M. Wu, Z. Fang, X. Chi, X. Chen, Y. Zhang and X. Wang, *Angew. Chem., Int. Ed.*, 2021, **60**, 16355–16359.
- 12 P. B. Pati, G. Damas, L. Tian, D. L. A. Fernandes, L. Zhang, I. B. Pehlivan, T. Edvinsson, C. M. Araujo and H. Tian, *Energy Environ. Sci.*, 2017, **10**, 1372–1376.
- 13 C. Krishnaraj, H. Sekhar Jena, L. Bourda, A. Laemont, P. Pachfule, J. Roeser, C. V. Chandran, S. Borgmans, S. M. J. Rogge, K. Leus, C. V. Stevens, J. A. Martens, V. Van Speybroeck, E. Breyneert, A. Thomas and P. Van Der Voort, *J. Am. Chem. Soc.*, 2020, **142**, 20107–20116.
- 14 X. Zhang, P. Ma, C. Wang, L.-Y. Gan, X. Chen, P. Zhang, Y. Wang, H. Li, L. Wang, X. Zhou and K. Zheng, *Energy Environ. Sci.*, 2022, **15**, 830–842.





