

INORGANIC CHEMISTRY

FRONTIERS

RESEARCH ARTICLE



Cite this: *Inorg. Chem. Front.*, 2015, 2, 949

Self-supported composites of thin Pt–Sn crosslinked nanowires for the highly chemoselective hydrogenation of cinnamaldehyde under ambient conditions†

Lin-Xiu Dai, Wei Zhu, Mu Lin, Zhi-Ping Zhang, Jun Gu, Yu-Hao Wang and Ya-Wen Zhang*

Alloying a second metal in a parent metal is an efficient way to improve the catalytic performances of monometallic nanocatalysts, thus the understanding of the alloying effects on the catalytic properties of bimetallic nanocatalysts is of great significance. Herein, we demonstrate the synthesis of self-supported composites of thin (*ca.* 3.8 nm) Pt–Sn crosslinked nanowires (PtSn/SnO₂ CNs) with a Pt : Sn molar ratio of 3–4 : 1 *via* a one-pot hydrothermal method. The growth mechanism of the CNs consisted of spontaneous hydrolysis and reduction of metal ions in water solution and the subsequent oriented attachment of M(OH)_x (M = Pt, Sn) particulate species under reduction by poly(vinylpyrrolidone) during hydrothermal processing. The nature of metal precursors, capping reagents and reduction rate has shown great influences on the shaping of the nanocatalysts into CNs. The PtSn/SnO₂ catalyst exhibited 87% selectivity (superior over pure Pt nanoparticles (NPs) and physical mixtures of Pt and SnO₂ NPs) under ambient conditions for the hydrogenation of cinnamaldehyde, owing to the formation of a Pt–Sn alloy in the CNs. The PtSn/SnO₂ catalyst also showed good recyclability and stability in chemoselectivity for cycle experiments of the catalysts.

Received 24th July 2015,
Accepted 31st August 2015

DOI: 10.1039/c5qi00129c
rsc.li/frontiers-inorganic

Introduction

Noble metal catalysts play an important role in the areas of energy conversion and storage, environmental improvement, organic catalysis and sensors, *etc.*¹ In order to minimize the usage of noble metals and promote the catalytic performance (activity, selectivity and durability), bimetallic catalysts have attracted tremendous attention from chemists to material scientists. It has been demonstrated that the bi-function effect, surface atom arrangement and electronic structure essentially affect the catalytic performance of bimetallic catalysts. With the control over the surface chemistry (*e.g.*, element ratio, oxidation state, exposed facets, lattice strain, proportion of corner/edge atoms, *etc.*) of bimetallic catalysts, which can be realized *via* various synthetic protocols of nanomaterials, elev-

ated catalytic properties of bimetallic catalysts are achieved as a result of the optimized adsorptions and desorptions of reactants and products.^{2–14}

Based on the universal growth mechanism of nanocrystals, well-developed wet chemistry synthetic methods offer a valid way for the preparation of uniform bimetallic nanocrystals with well-defined structures. The prompt development of shape-controlled synthetic strategies of nanocatalysts boosts the fundamental studies of catalysis as well as the constructions of highly efficient and highly durable nanocatalysts with novel structures. The reaction sites that determine the catalytic properties of a catalyst can be identified when shape-controlled nanocrystals are used as catalysts. Till now, many solution based synthetic approaches have been used to prepare bimetallic NPs with various morphologies, including nanowires, nanoplates, nanodendrites, cubes, polyhedrons, *etc.*^{15–23} Previous reports have pointed that nanowires possess excellent structure stability, high density of structural defects and good recyclability, resulting in significant improvement of performances in heterogeneous catalysis (*e.g.*, ethanol electro-oxidation, formic acid oxidation and hydrogenation reactions of cinnamaldehyde (CAL), nitrobenzene or styrene, *etc.*).^{16,22}

Selective hydrogenation of α,β -unsaturated aldehydes to unsaturated alcohols is a commercially important industrial

Beijing National Laboratory for Molecular Sciences, State Key Laboratory of Rare Earth Materials Chemistry and Applications, PKU-HKU Joint Laboratory in Rare Earth Materials and Bioinorganic Chemistry, College of Chemistry and Molecular Engineering, Peking University, Beijing 100871, China. E-mail: ywzhang@pku.edu.cn; Fax: +86-10-62756787; Tel: +86-10-62756787

† Electronic supplementary information (ESI) available: TEM images of PtSn/SnO₂ catalysts, spectra of FTIR and Rietveld refinement of PXRD. See DOI: [10.1039/c5qi00129c](https://doi.org/10.1039/c5qi00129c)

process of fragrance and pharmaceutical fields.^{24,25} Designing catalysts for both high activity and selectivity is still a crucial challenge in heterogeneous catalysis research, particularly for the selective hydrogenation of α,β -unsaturated aldehydes. Pt-based nanomaterials are the most widely studied catalysts for fuel cell,¹ three-way catalysis²⁶ and catalytic hydrogenation.²⁷ Pt serves as the main active site for hydrogenation. Smaller Pt nanoparticles with low coordination sites favor the hydrogenation of the C=C bond,²⁸ and the selective hydrogenation does not occur on the clean surface of Pt (111).²⁹ Thus, monometallic Pt NPs showed high hydrogenation activity but low selectivity to unsaturated alcohols for the selective hydrogenation of α,β -unsaturated aldehydes. Therefore, it is necessary to improve the selectivity by modifying the Pt-based surface of the catalysts.

The strategy of introducing second metals such as Fe, Co, Cu, Ni and Sn into Pt is widely used to increase hydrogenation selectivity to unsaturated alcohols.^{30–36} The second metals were utilized to change the electronic structure and the surface atomic arrangement of Pt-based alloys. As an example of the Pt–Sn alloy, experimental and computational investigations have demonstrated that the adsorption energy of α,β -unsaturated aldehydes on the (111) facet of Pt–Sn alloys is significantly weaker than that on the (111) facet of Pt.^{37–39} On the alloy surfaces, an oxygen–tin interaction is more stable than the C=O bonding with a Pt surface. Density functional theory (DFT) has proved that the addition of tin in Pt led to the atop adsorption mode of α,β -unsaturated aldehydes, thus favoring the hydrogenation of the C=O bond.⁴⁰ Several researches have explored the composition-dependent catalytic performances of Pt-based catalysts. On doping a second metal (Ti, Mn, Fe, Co, Ni, Cu, Zn, Sn, Pb) to Pt, the selectivity presented a volcano trend, suggesting changes in the electronic structure of Pt.³² Actually, the controlling of particle size, shape and atomic segregation changed the alloying effects to different degrees, thus resulting in the improvement of selectivity.^{41,42} Hence, rationally regulating electronic and geometrical structures to activate certain functionalities of α,β -unsaturated aldehydes could overcome thermodynamically favorable C=C hydrogenation over C=O hydrogenation. Moreover, support effects can be utilized to enhance the stability and activity of main catalysts.^{43–45} Recent research studies have manifested that bimetallic catalysts achieved 99% selectivity to unsaturated alcohol for CAL hydrogenation. Nevertheless, the high catalytic selectivity was acquired under the conditions of high temperature and high H₂ pressure.³² The harsh reaction conditions normally have a high demand for the structure stability of catalysts.

Herein, we report on the synthesis of self-supported composites of thin Pt–Sn crosslinked nanowires by a facile one-pot hydrothermal method. With the as-prepared PtSn/SnO₂ CNs, high chemoselectivity to unsaturated alcohols under ambient reaction conditions for CAL hydrogenation has been achieved. The PtSn/SnO₂ composites exhibited 87% selectivity to cinnamyl alcohol (COL) without significant loss in activity. It was deduced that the formation of a Pt–Sn alloy in the CNs probably changed the electronic structure

of Pt, thus favoring the activation of the C=O bond during the CAL hydrogenation.

Experimental section

Chemicals

H₂PtCl₆·6H₂O (A.R., Sinopharm Chemical Reagent Co. Ltd, China), K₂PtCl₄ (A.R., Beijing Tongguang Fine Chemicals Company), SnCl₂·2H₂O (A.R., Xilong Chemical Co. Ltd, China), SnCl₄·5H₂O (A.R., Beijing Chemical Works, China), poly(vinyl-pyrrolidone) (PVP: M_w = 29 000 and 55 000, Sigma-Aldrich), ethylene glycol (extra pure, J&K), cinnamaldehyde (Shanghai Shuangxiang Chemical Works, China), naphthalene (A.R., Beijing Chemical Works, China), ethyl ether (A.R., Beijing Tongguang Fine Chemicals Company), HCl solution (A.R., Xilong Chemical Co. Ltd, China), ethanol (A.R.), acetone (A.R.), cyclohexane (A.R.), and deionized water (Millipore, 18.2 MΩ cm).

Synthesis of PtSn/SnO₂ CNs

The precursors, 0.05 mmol of H₂PtCl₆, 0.07 mmol of SnCl₂·2H₂O, 100 mg of PVP (M_w = 55 000), and 0.3 mmol of HCl (1.0 mol L⁻¹) were dissolved in 15 mL of deionized water with stirring for 20 min. The solution was transferred to a 25 mL Teflon-lined stainless steel autoclave and heated at 180 °C for 12 h. After the mixture was cooled, the black products were centrifuged by mixing 40 mL of acetone and washed with ethanol/acetone twice, and lastly dispersed in ethanol for further characterization.

Synthesis of SnO₂ NPs

The synthesis of SnO₂ NPs was similar to that of PtSn/SnO₂ CNs except for the absence of H₂PtCl₆.

Synthesis of Pt NPs

0.06 mmol of K₂PtCl₄ and 100 mg of PVP (M_w = 29 000) were mixed in 15 mL of ethylene glycol with stirring for 20 min. The solution was transferred to a 25 mL Teflon-lined stainless steel autoclave and held at 180 °C for 24 h. The obtained black products were centrifuged and washed with the addition of 40 mL of acetone and 3 mL cyclohexane several times, and lastly dispersed in ethanol for further characterization.

Cinnamaldehyde hydrogenation reaction studies

CAL hydrogenation was run in a reaction tube (2.5 cm in diameter) with a solution of 0.5 mmol of cinnamaldehyde, 2.5 mL of ethanol and catalysts (0.0025 mmol, 0.5 mol%). After being purged with H₂, the reaction mixture was stirred at 25 °C under a H₂ atmosphere (1 bar). The as-obtained products were quantitatively determined by GC with 0.5 mmol of naphthalene as the internal standard.

Instrumentation

Transmission electron microscopy (TEM), high-resolution transmission electron microscopy (HRTEM), energy dispersive

X-ray spectroscopy (EDS), and high-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM) EDS spot scan analysis were conducted on a FEG-TEM (JEM-2100F, JEOL, Japan) operated at 200 kV. The samples for TEM characterization were prepared by dropping the colloid solution on copper grids coated with amorphous carbon and drying naturally. Powder X-ray diffraction (PXRD) analysis was performed on a Rigaku D/MAX-2000 diffractometer (Japan). Inductively coupled plasma atomic emission spectroscopy (ICP-AES) analysis was conducted on a Profile Spec ICP-AES spectrometer (Leeman, U.S.A.). X-ray photoelectron spectroscopy (XPS) analysis was performed on an Axi Ultra imaging photoelectron spectrometer (Kratos, UK). All gas chromatography spectrometry experiments were carried out and recorded by GC (GC 7890A, Agilent Technologies).

Results and discussion

Hydrothermal synthesis and structural characterization of PtSn/SnO₂ CNs

The PtSn/SnO₂ CNs were prepared *via* hydrothermal synthesis at 180 °C. The redox process occurred between H₂PtCl₆ and SnCl₂ solution. PVP served as the capping agent to obtain PtSn/SnO₂ CNs. The TEM image in Fig. 1a shows that the samples appeared in the shape of cross-linked nanowires. The width of the CNs was 3.8 ± 1.0 nm. HAADF-STEM-EDS was used to analyze the elemental distribution of Pt and Sn in a single nanowire. Fig. 1b shows that the atom ratio of Pt and Sn was about 3–4 : 1 for PtSn/SnO₂ CNs. Uniform Pt-rich elemen-

tal distribution was found on both the branches and the nodes of nanowires. In addition, the PXRD pattern of the as-prepared composites in Fig. 1c was attributed to the co-existing fcc Pt phase (JCPDS no. 04-0802) and the tetragonal SnO₂ phase (JCPDS no. 41-1445). The PXRD data were further quantitatively analysed by Rietveld refinement in TOPAS 3.0 (Table S1 and Fig. S1 in ESI†), indicating a weight ratio of 3 : 2 for Pt₃Sn and SnO₂. The (111) peak position (39.19°) of the fcc-structured portion of composites fell in between that of Pt (39.76°) and that of Pt₃Sn (38.94°), suggesting the formation of a Pt–Sn alloy with a Pt : Sn molar ratio of more than 3 : 1 in the CNs.

As shown in the HRTEM image of CNs in Fig. 1d, the CNs were crystallized to some extent. The lattice fringes of SnO₂ were hardly found on the nanowires because of the segregation of SnO₂ from the nanoaggregates in the products. The nanoaggregates with a Pt : Sn molar ratio of 1 : 4 were found in TEM images (Fig. S2 in ESI†), as proved by the observable lattice fringes for {110}, {101} and {211} of tetragonal SnO₂.

XPS spectra (Fig. 2a) show that Pt⁴⁺ ions in precursors were reduced to Pt⁰ and Pt²⁺ with a ratio of 60 : 40 in the CN composites. As illustrated in Fig. 2b, the XPS Sn 3d_{5/2} peaks at 486.9 eV suggested that Sn was mainly in the oxidized state.

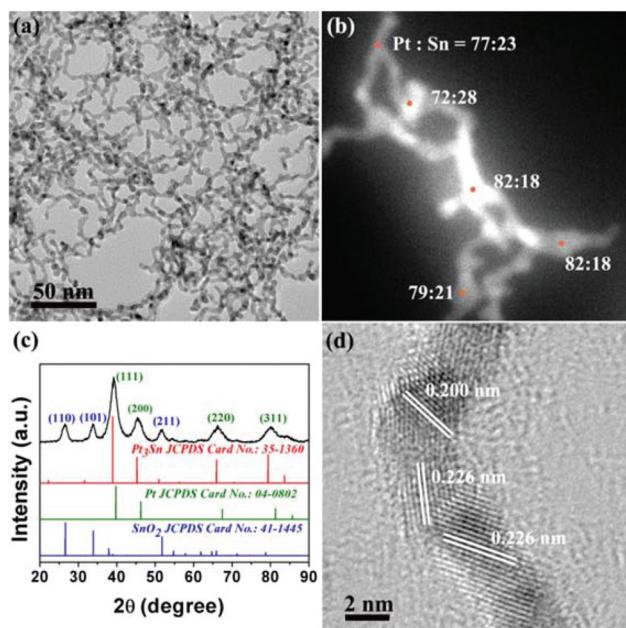


Fig. 1 TEM image (a), EDS spot scan image (b), PXRD pattern (c) and HRTEM image (d) of the as-obtained composites. For (c), marked lattice facets in dark blue belong to SnO₂, green ones belong to Pt.

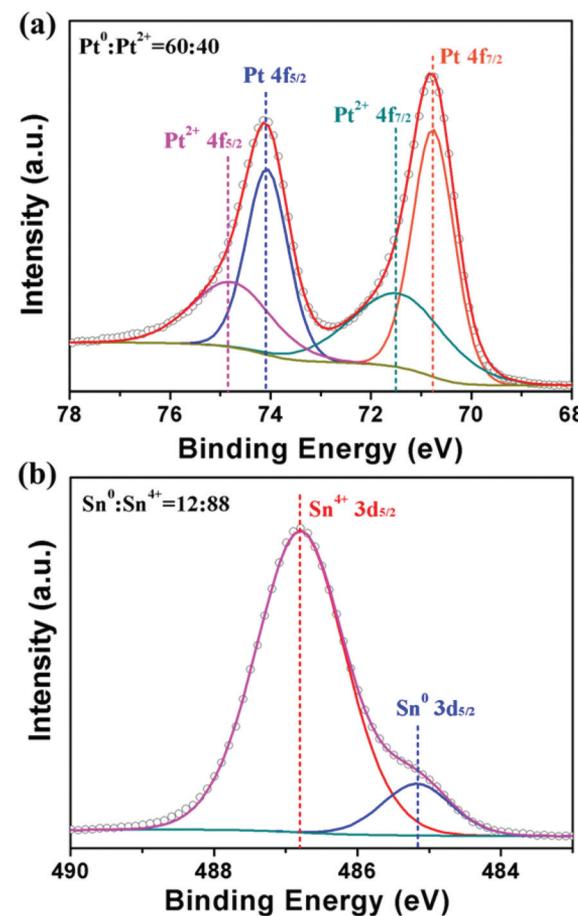


Fig. 2 XPS spectra of the as-obtained products for Pt 4f (a) and Sn 3d_{5/2} (b).

However, according to the literature data,⁴⁶ the peaks assignable to tin(II) and tin(IV) overlap. It is difficult to assign the peaks to Sn²⁺ or Sn⁴⁺ only on the basis of the observed binding energy value. Considering the absence of SnO in the PXRD pattern of Fig. 1c, the oxidized tin ought to be Sn⁴⁺.⁴⁷ The result of 12% Sn⁰ observed at a binding energy of 485.2 eV implied the formation of a Pt–Sn alloy in the CNs, consistent with the negative shift of main peaks in PXRD data. Hence, the above characterization results clarified that the obtained products consisted of PtSn/SnO₂ CNs with a Pt:Sn molar ratio of 3–4:1 and nanoaggregates.

The growth mechanism of PtSn/SnO₂ CNs

To further explore the formation mechanism of PtSn/SnO₂ CNs, we carried out a battery of condition experiments with the help of TEM characterization. The results demonstrated that the growth mechanism of PtSn/SnO₂ CNs was closely related to reaction time as well as starting materials such as metal precursors, raw material ratio, reductants and capping reagents. In order to design a bimetallic catalyst with strong interaction between two metals on the atomic scale, Pt⁴⁺ (H₂PtCl₆) and Sn²⁺ (SnCl₂) were used as the preferred metal precursors in view of the redox process of Pt⁴⁺ and Sn²⁺. From the standard electrode potential of Pt⁴⁺ and Sn²⁺ (φ^0 Pt(iv)/Pt(0) = 0.93 V, φ^0 Sn(IV)/Sn(II) = 0.15 V), a redox reaction (Pt⁴⁺ + Sn²⁺ → Pt + Sn⁴⁺) should take place. When SnCl₂·2H₂O was added into H₂PtCl₆ solution, the light yellow solution became brick red, and the centrifuged products were further characterized by XPS. Fig. 3a shows that the ratio of Pt²⁺ and Pt⁴⁺ is 79:21 (without Pt⁰), indicating that incomplete reduction occurred at room temperature. From the XPS spectrum of Sn 3d_{5/2}, no metallic Sn⁰ was found in Fig. 3b, indicating that the addition of PVP and the high temperature reduction (180 °C) played important roles in the reduction of tin ions and the formation of a Pt–Sn alloy at later periods.

Fig. 4 shows different morphologies of the products resulting from using different combination of metal precursors in the synthesis. The adoption of H₂PtCl₆/SnCl₄, K₂PtCl₄/SnCl₄ and K₂PtCl₄/SnCl₂ did not produce any nanowires within 12 h of reaction (Fig. 4a–c). When the reaction time was prolonged to 24 h, nanowires appeared only with using H₂PtCl₆/SnCl₄ or K₂PtCl₄/SnCl₄ as the metal precursors, as shown in Fig. S3a and S3b in the ESI.† However, the combination of H₂PtCl₆/SnCl₂ could produce CNs after the reactions from 12 h (Fig. 4d) to 24 h (Fig. S3d in the ESI†). On taking K₂PtCl₄ and SnCl₂ as metal precursors, the Pt²⁺ ions were rapidly reduced and grew into isolated NPs after the initial reaction (Fig. S3c in the ESI†). Then, tin ions were reduced to Sn⁰ in the later stage, resulting in the appearance of dispersed NPs. Therefore, it was deduced that the formation of nanowires highly depended on the generation of more platinum and tin hydroxyl species.

In addition, the influence of the ratio of the two metal precursors, H₂PtCl₆ and SnCl₂, was also studied. Only when the molar ratio of Pt⁴⁺ and Sn²⁺ in precursors was in the range of 1:1 to 2:1, CNs could be synthesized (Fig. 5b and c). When the molar ratio was more than 2, the reduction of excess Pt⁴⁺

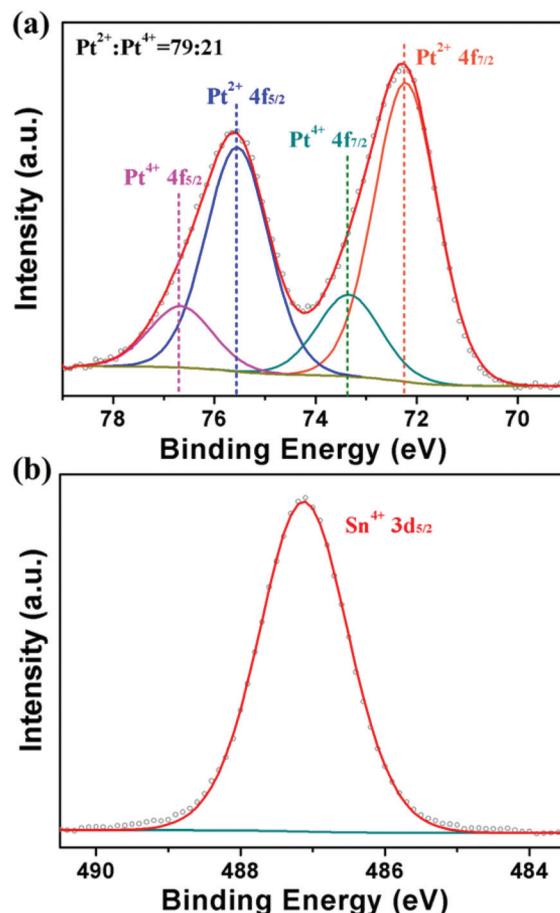


Fig. 3 XPS spectra of the as-obtained products for Pt 4f (a) and Sn 3d_{5/2} (b) after mixing two metal precursors with stirring for 20 min.

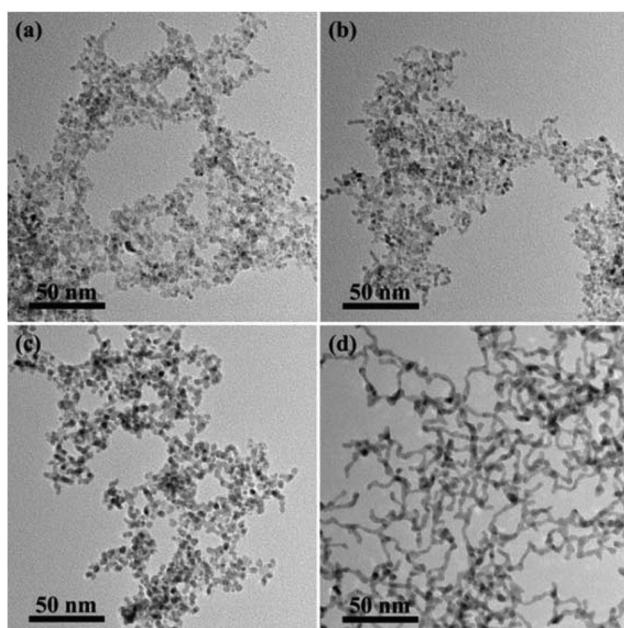


Fig. 4 TEM images of the products using H₂PtCl₆ and SnCl₄ (a), K₂PtCl₄ and SnCl₄ (b), K₂PtCl₄ and SnCl₂ (c) and H₂PtCl₆ and SnCl₂ (d) as metal precursors after 12 h reaction.

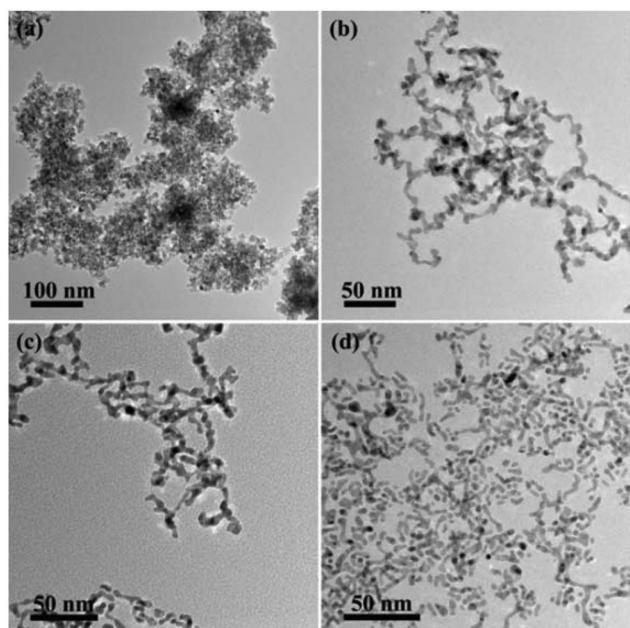


Fig. 5 TEM images of the products using different ratios of H_2PtCl_6 and SnCl_2 as metal precursors: (a) 1 : 2, (b) 1.5 : 1, (c) 2 : 1 and (d) 3 : 1.

ions was mainly assisted by PVP. The probably weakened interaction between Pt and Sn caused the formation of isolated particles (Fig. 5d). On the other hand, more SnO_2 NPs appeared if excess Sn^{2+} ions in precursors were introduced. Less attachment between platinum and tin hydroxyl species produced more SnO_2 NPs to form SnO_2 -supported Pt NPs.

Then, we tried to use PVP and ascorbic acid (AA) as the alternative reductants to elaborate the influence of the reduction rate. As shown in Fig. 6a, only large Pt NPs appeared without the addition of PVP due to the lack of capping agents to prevent the aggregation of the NPs, while no significant influence on the nanowire structures was observed with the addition of excessive PVP. AA has stronger reducibility than PVP, probably resulting in a faster reduction rate. As illustrated

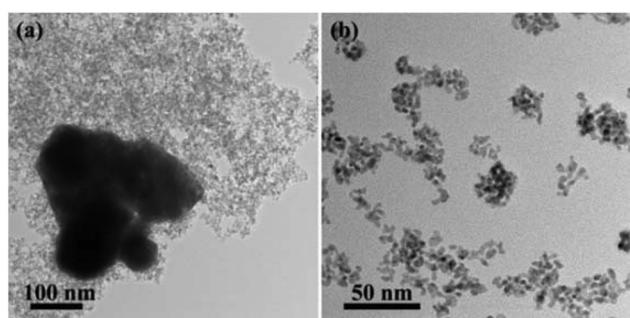


Fig. 6 TEM images of the products using no PVP (a) and 100 mg PVP + 176 mg AA (b). The synthetic conditions are the same as the synthesis of PtSn/SnO_2 CNs.

in Fig. 6b, the addition of AA led to the formation of small NPs. It was because more nuclei resulted from the faster reduction rate of the metal precursors, which led to the prompt aggregation of the nuclei, and thus retarded the formation of CNs. Hence, the kinetic-controlled formation of nanowire structures required a modest reduction rate of metal precursors with PVP serving as both the capping reagent and the reductant.

As shown in the FTIR spectra (Fig. S4 in the ESI†), the appearance of the vibration peak of $\text{C}=\text{O}$ at 1642 cm^{-1} for the composites indicated the existence of a trace amount of PVP on the surfaces of the CNs. A red shift of *ca.* 24 cm^{-1} in the vibration peak of $\text{C}=\text{O}$ compared with that of pure PVP was attributed to the coordination of PVP molecules with PtSn/SnO_2 CNs by their O atoms.⁴⁸

To further understand the growth mechanism of PtSn/SnO_2 CNs, the time of the hydrothermal reaction was varied to observe the morphology evolution of the CNs in the synthesis process. Fig. 7 shows the TEM images of the time-sequence synthesis process. In the first 0.5 h, only a number of small NPs appeared. As the reaction time went on, these small NPs were attached to form short nanowires. After 12 h reaction, PtSn/SnO_2 CNs were obtained. By further extending the reaction time to 24 h, we did not observe a morphological change of CNs. The growth mechanism of the CNs was speculated to be similar to the sol-gel process.⁴⁹ Redox reaction and spontaneous hydrolysis of Pt ions and Sn ions took place to form metal hydroxyl species at the beginning, then, these metal hydroxyl species proceed towards the oriented attachment of surface hydroxyl groups to produce PtSn/SnO_2 CNs under the


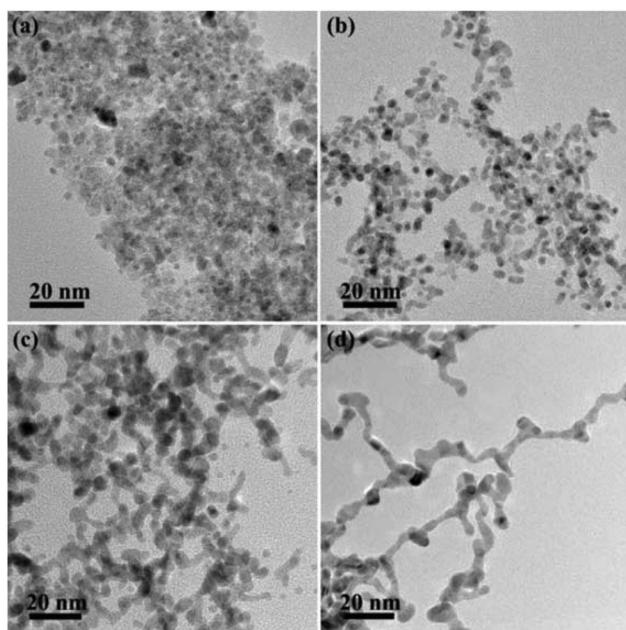


Fig. 7 TEM images of PtSn/SnO_2 CNs synthesized at $180\text{ }^\circ\text{C}$ for 0.5 h (a), 2 h (b), 4 h (c) and 24 h (d).

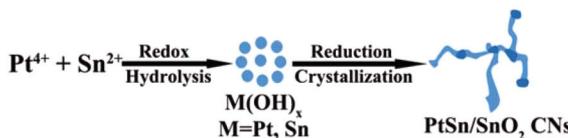

Scheme 1 The growth mechanism of PtSn/SnO₂ CNs.

reduction by PVP at 180 °C, residual oxidized tin constituted nanoaggregates. As shown in Scheme 1, the growth mechanism is the integration of the redox reaction and the self-organization process.

Catalytic performance in the hydrogenation reaction


The selective hydrogenation of cinnamaldehyde was employed to evaluate the catalytic performances of PtSn/SnO₂ CNs (Scheme 2). In the catalytic tests, Pt NPs in the size of 3.1 ± 0.5 nm, and SnO₂ NPs in the size of 7.8 ± 2.0 nm, and physical mixtures of Pt and SnO₂ (Pt + SnO₂ NPs) prepared *via* a similar hydrothermal method, were used as references (Fig. S5 in the ESI†).

In this reaction, hydrogenation on the C=O bond and the C=C bond generally led to a parallel and consecutive hydrogenation reduction to obtain different catalytic products. The formation of the HCAL is favored over the COL because of thermodynamics.⁵⁰ The distribution of the three hydrogenation products depends on the structure and composition of catalysts.⁵¹

From the results of experiments, CAL was completely converted by Pt NPs, PtSn/SnO₂ CNs and Pt + SnO₂ NPs with the addition of the same amount of Pt atoms (determined by ICP-AES) in 12 h. No hydrogenation activity was observed for SnO₂ NPs, demonstrating the role of Pt as the main active site. For the PtSn/SnO₂ CNs, SnO₂ as the supporter improved the physical stability of the catalyst, but contributed little to the overall hydrogenation activity. As shown in Table 1, we calculated the mass activity of the three catalysts, the mass activity was defined as below:

$$\text{Mass activity} = \text{mmol}_{\text{CAL}} \text{ converted min}^{-1} \text{ mmol}_{\text{Pt}}^{-1}$$

From Table 1, it is seen that the mass activities of the three catalysts were comparable.

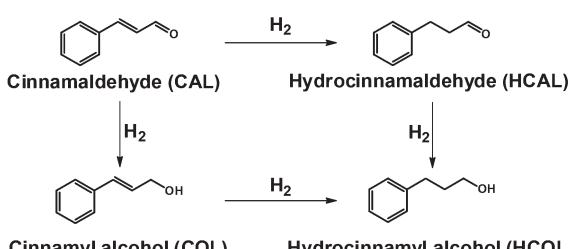

Scheme 2 Reaction paths for the hydrogenation of cinnamaldehyde.

Table 1 Cinnamaldehyde hydrogenation with PtSn/SnO₂ CNs, Pt NPs and Pt + SnO₂ NPs

Catalysts	Time [min]	Conversion [%]	n_{Pt} [μmol]	Mass activity [min ⁻¹]
PtSn/SnO ₂ CNs	4	10	2.5	4.7
Pt NPs	4	15	2.5	6.4
Pt + SnO ₂ NPs	4	12	2.5	5.7

Fig. 8a shows the selectivity of the nanocatalysts for the CAL hydrogenation, and the selectivity was defined as below:

$$\% \text{Selectivity} = [\text{COL}] / (\text{COL} + \text{HCAL} + \text{HCOL}) \times 100$$

PtSn/SnO₂ CNs exhibited 87% selectivity to COL in ethanol at room temperature under 1 bar of H₂, while the other catalysts could not catalyze the hydrogenation of CAL to COL under this condition.

As is known, molecular hydrogen is adsorbed and dissociated on surface Pt sites. The adsorption geometry of the C=C bond and the C=O bond is highly dependent on the surface structure of catalysts and the molecular structure of α,β -unsaturated aldehyde.⁵² CAL generally adopted a flat-lying co-adsorption geometry on the Pt surface.⁵³ Pure Pt or supported Pt catalysts are well known for their activity of olefin hydrogenation, implying more favorable binding with C=C

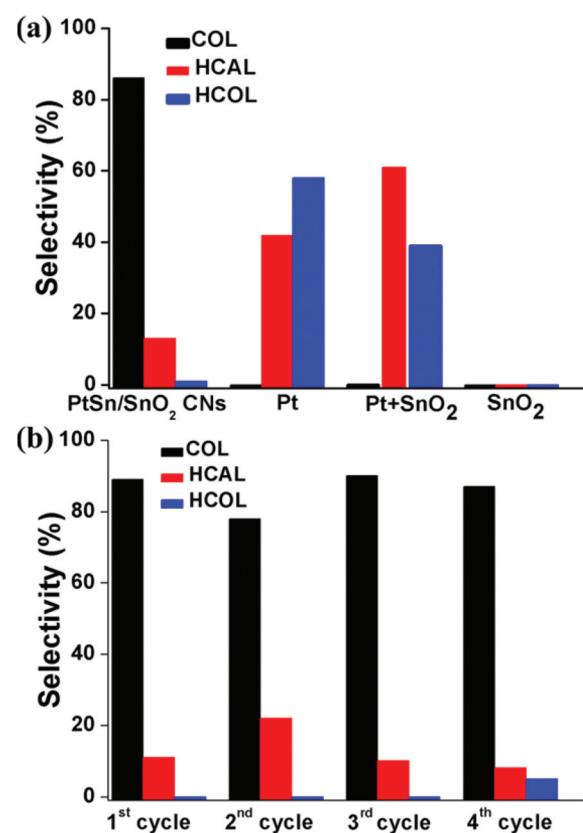


Fig. 8 Selectivity (a) and stability (b) for cinnamaldehyde hydrogenation.

than C=O. So the low selectivity of Pt NPs and Pt + SnO₂ NPs was caused by the strong adsorption of the C=C bond and more rapid hydrogenation rate, and high desorption energy resulted in the formation of complete hydrogenation products (*i.e.*, HCOL).⁵²

However, the selectivity to COL of PtSn/SnO₂ CNs was as high as 87%, possibly because of the formation of a Pt–Sn alloy.^{37–39} The introduction of electropositive metals such as Sn, could increase the electron density on Pt, which decreased the capability for C=C bond adsorption and increased the interaction of the C=O bond with the polar bimetallic sites.⁵⁴ The oxygen of carbonyl has a stronger chemical affinity with Sn than that with Pt, thus an atop adsorption mode of α,β -unsaturated aldehydes would be more favorable, as confirmed by both experimentation and DFT studies.⁴⁰ In an upright adsorption configuration, the successive hydrogenation of COL to HCOL does not take place on the alloy as it does on platinum, because no activation of C=C occurs. In particular for nanowire catalysts with lots of unsaturated coordination sites, the upright adsorption geometry was more reasonable.^{55,56}

Previous research studies have emphasized that the low desorption energy of COL on the Pt–Sn alloy is another reason for high selectivity to unsaturated alcohols, which reduces the possibility of the complete hydrogenation to HCOL.⁵⁷ The physical mixtures of Pt and SnO₂ showed a similar selectivity with pure Pt NPs, indicating the lack of the ensemble effect of alloying structures on the atom scale. When partial Pt atoms on the surface were replaced by Sn, the adsorption configuration was likely changed. As the number of Sn atoms increased on the surface, higher selectivity was realized.⁵⁸ For PtSn/SnO₂ CNs, SnO_{2-x} is also responsible for high selectivity to COL, because the oxygen vacancy sites provided by SnO_{2-x} could enhance the adsorption of the C=O group.⁵⁹ In addition, although monometallic Pt exhibited the negative effect of unsaturated coordination sites on selective hydrogenation of α,β -unsaturated aldehydes, Pt-based bimetallic catalysts with many unsaturated coordination atoms benefited the formation of COL.²⁸

The stability of PtSn/SnO₂ CNs was also investigated by injecting reactants repeatedly after complete conversion of CAL and retaining the PtSn/SnO₂ CNs for the next run of the reaction. There was no obvious decrease in the conversion between the reused catalysts for the first three cycles. Full conversion of CAL required the double reaction time in the fourth cycle possibly due to the partial disassembly of nanowire structures after 3 cycles (Fig. S6 in the ESI†). Fig. S7 in the ESI† indicated that Pt NPs and Pt + SnO₂ NPs also underwent significant aggregation after 1 cycle, suggesting the enhanced structural stability of the PtSn/SnO₂ CNs. As shown in Fig. 8b, PtSn/SnO₂ CNs still possessed about 90% selectivity for 4 cycles, possibly owing to the structural stability of the self-supported CNs under the reaction conditions.

ICP-AES tests evidenced no detectable metal leaching, while control experiments verified negligible CAL conversion in the absence of either H₂ or Pt, confirming the heterogeneous nature of the observed reactions and the high durability and

recyclability of PtSn/SnO₂ CNs during the selective hydrogenation of cinnamaldehyde.

Conclusion

In this work, we prepared self-supported composites of thin Pt–Sn CNs with a Pt:Sn molar ratio of 3–4:1, by the oriented attachment mechanism *via* a facile hydrothermal method. The growth of the CNs was revealed to proceed by the following two stages: spontaneous hydrolysis and reduction of metal ions in water solution and the subsequent oriented attachment of M(OH)_x (M = Pt, Sn) particulate species under the reduction by poly(vinylpyrrolidone) during hydrothermal treatment. For the selective hydrogenation of CAL, the PtSn/SnO₂ CNs showed the highest selectivity to unsaturated alcohols with little loss of activity under ambient conditions. It was deduced that the electronic and geometric effects of the Pt–Sn alloy benefited the activation of the C=O bond in the CNs, and decreased the desorption energy of unsaturated alcohols. In addition, the observed prominent durability and recyclability could reflect the intrinsic property of the self-supported nanowire structure. Hence, the self-supported thin Pt–Sn CNs combine the merits of a bimetallic alloy with a nanowire structure having a high portion of step/edge atoms for the CAL hydrogenation reaction with high selectivity and good durability. This work shed new light on the design of high-performance bimetallic catalysts by modulating the alloying effect of bimetallics as well as dimensionality of nanostructures.

Acknowledgements

This work was supported by the National Science Foundation of China (NSFC) (Grant No. 21025101, 21271011, 21573005, and 21321001). Y.W.Z. particularly appreciates the financial aid of China National Funds for Distinguished Young Scientists from the NSFC.

Notes and references

- 1 G. A. Somorjai, *Chem. Rev.*, 1996, **96**, 1223.
- 2 V. R. Stamenkovic, B. S. Mun, M. Arenz, K. J. J. Mayrhofer, C. A. Lucas, G. F. Wang, P. N. Ross and N. M. Markovic, *Nat. Mater.*, 2007, **6**, 241.
- 3 M. S. Chen, D. Kumar, C.-W. Yi and D. W. Goodman, *Science*, 2005, **310**, 291.
- 4 P. Strasser, S. Koh, T. Anniyev, J. Greeley, K. More, C. F. Yu, Z. C. Liu, S. Kaya, D. Nordlund, H. Ogasawara, M. F. Toney and A. Nilsson, *Nat. Chem.*, 2010, **2**, 454.
- 5 V. R. Stamenkovic, B. Fowler, B. S. Mun, G. F. Wang, P. N. Ross, C. A. Lucas and N. M. Marković, *Science*, 2007, **315**, 493.
- 6 K.-Q. Sun, Y.-C. Hong, G.-R. Zhang and B.-Q. Xu, *ACS Catal.*, 2011, **1**, 1336.

7 F. Gao and D. W. Goodmanz, *Chem. Soc. Rev.*, 2012, **41**, 8009.

8 H. Zhang, M. S. Jin and Y. N. Xia, *Chem. Soc. Rev.*, 2012, **41**, 8035.

9 J. B. Wu, P. P. Li, Y.-T. Pan, S. Warren, X. Yin and H. Yang, *Chem. Soc. Rev.*, 2012, **41**, 8066.

10 J. Gu, Y.-W. Zhang and F. Tao, *Chem. Soc. Rev.*, 2012, **41**, 8050.

11 M. Sankar, N. Dimitratos, P. J. Miedziak, P. P. Wells, C. J. Kiely and G. J. Hutchings, *Chem. Soc. Rev.*, 2012, **41**, 8099.

12 Y. Pei, G. B. Zhou, N. Luan, B. N. Zong, M. H. Qiao and F. Tao, *Chem. Soc. Rev.*, 2012, **41**, 8140.

13 Y. W. Zhang, W. Y. Huang, S. E. Habas, J. N. Kuhn, M. E. Grass, Y. Yamada, P. D. Yang and G. A. Somorjai, *J. Phys. Chem. C*, 2008, **112**, 12092.

14 F. Tao, M. E. Grass, Y. W. Zhang, D. R. Butcher, F. Aksoy, S. Aloni, V. Altoe, S. Alayoglu, J. R. Renzas, C.-K. Tsung, Z. W. Zhu, Z. Liu, M. Salmeron and G. A. Somorjai, *J. Am. Chem. Soc.*, 2010, **132**, 8697.

15 J. Gu, G. X. Lan, Y. Y. Jiang, Y. S. Xu, W. Zhu, C. H. Jin and Y. W. Zhang, *Nano Res.*, 2015, **8**, 1480.

16 J. B. Ding, L. Z. Bu, N. Zhang, J. L. Yao, Y. Huang and X. Q. Huang, *Chem. – Eur. J.*, 2015, **21**, 3901.

17 A. Rai, M. Chaudhary, A. Ahmad, S. Bhargava and M. Sastry, *Mater. Res. Bull.*, 2007, **42**, 1212.

18 X. L. Wang, B. H. Wu, G. X. Chen, Y. Zhao, P. X. Liu, Y. Dai and N. F. Zheng, *Nanoscale*, 2014, **6**, 6798.

19 D.-Y. Wang, H.-L. Chou, C.-C. Cheng, Y.-H. Wu, C.-M. Tsai, H.-Y. Lin, Y.-L. Wang, B.-J. Hwang and C.-C. Chen, *Nano Energy*, 2015, **11**, 631.

20 J. Zhang and J. Y. Fang, *J. Am. Chem. Soc.*, 2009, **131**, 18543.

21 A.-X. Yin, X.-Q. Min, W. Zhu, H.-S. Wu, Y.-W. Zhang and C.-H. Yan, *Chem. Commun.*, 2012, **48**, 543.

22 Q. Yuan and X. Wang, *Nanoscale*, 2010, **2**, 2328.

23 B. Lim, M. J. Jiang, P. H. C. Camargo, E. C. Cho, J. Tao, X. M. Lu, Y. M. Zhu and Y. N. Xia, *Science*, 2009, **324**, 1302.

24 P. Gallezot and D. Richard, *Catal. Rev. Sci. Eng.*, 1998, **40**, 81.

25 L. A. Saudan, *Acc. Chem. Res.*, 2007, **40**, 1309.

26 H. He, H. X. Dai, L. H. Ng, K. W. Wong and C. T. Au, *J. Catal.*, 2002, **206**, 1.

27 Y. E. Wu, S. F. Cai, D. S. Wang, W. He and Y. D. Li, *J. Am. Chem. Soc.*, 2012, **134**, 8975.

28 S. C. Tsang, N. Cailuo, W. Oduro, A. T. S. Kong, L. Clifton, K. M. K. Yu, B. Thiebaut, J. Cookson and P. Bishop, *ACS Nano*, 2008, **2**, 2547.

29 L. E. Murilloa and J. G. G. Chen, *Surf. Sci.*, 2008, **602**, 919.

30 W. T. Zang, G. Z. Li, L. Wang and X. W. Zhang, *Catal. Sci. Technol.*, 2015, **5**, 2532.

31 T. B. L. W. Marinelli, S. Nabuurs and V. Ponec, *J. Catal.*, 1995, **151**, 431.

32 W. O. Oduro, N. Cailuo, K. M. K. Yu, H. W. Yang and S. C. Tsang, *Phys. Chem. Chem. Phys.*, 2011, **13**, 2590.

33 Z. M. Rong, Z. H. Sun, Y. Wang, J. K. Lv and Y. Wang, *Catal. Lett.*, 2014, **144**, 980.

34 A. Stolle, T. Gallert, C. Schmöger and B. Ondruschka, *RSC Adv.*, 2013, **3**, 2112.

35 L. E. Murilloa, C. A. Menning and J. G. G. Chen, *J. Catal.*, 2009, **268**, 335.

36 R. Y. Zheng, M. D. Porosoff, J. L. Weiner, S. L. Lu, Y. X. Zhu and J. G. G. Chen, *Appl. Catal. A*, 2012, **419**, 126.

37 J. Haubrich, D. Loffreda, F. Delbecq, P. Sautet, Y. Jugnet, A. Krupski, C. Becker and K. Wandelt, *J. Phys. Chem. C*, 2008, **112**, 3701.

38 J. Haubrich, D. Loffreda, F. Delbecq, P. Sautet, A. Krupski, C. Becker and K. Wandelt, *J. Phys. Chem. C*, 2009, **113**, 13947.

39 J. Haubrich, D. Loffreda, F. Delbecq, P. Sautet, Y. Jugnet, C. Becker and K. Wandelt, *J. Phys. Chem. C*, 2010, **114**, 1073.

40 F. Delbecq and P. Sautet, *J. Catal.*, 2003, **220**, 115.

41 J. P. Stassi, P. D. Zgolycz, S. R. de Miguel and O. A. Scelza, *J. Catal.*, 2013, **306**, 11.

42 F. Colomaa, A. Sepúlveda-Escribanoa, J. L. G. Fierrob and F. R. Reinoso, *Appl. Catal. A*, 1996, **136**, 231.

43 J. J. Shi, R. F. Nie, P. Chen and Z. Y. Hou, *Catal. Commun.*, 2013, **41**, 101.

44 B.-H. Zhao, J.-G. Chen, X. Liu, Z.-W. Liu, Z. P. Hao, J. L. Xiao and Z.-T. Liu, *Ind. Eng. Chem. Res.*, 2012, **51**, 11112.

45 L. J. Durndell, C. M. A. Parlett, N. S. Hondow, M. A. Isaacs, K. Wilson and A. F. Lee, *Sci. Rep.*, 2012, **5**, 9425.

46 J. F. Moulder, W. F. Stickle, P. E. Sobol and K. D. Bomben, *Handbook of X-ray photoelectron spectroscopy*, Perkin-Elmer Corp., USA, 1992.

47 W.-Z. Hung, W.-H. Chung, D.-S. Tsai, D. P. Wilkinson and Y.-S. Huang, *Electrochim. Acta*, 2010, **55**, 2116.

48 H. S. Wang, X. L. Qiao, J. G. Chen, X. J. Wang and S. Y. Ding, *Mater. Chem. Phys.*, 2005, **94**, 449.

49 G. Z. Cao and Y. Wang, *Nanostructures and Nanomaterials: Synthesis, Properties, and Applications*, Imperial College Press, China, 2004.

50 C. Mohr and P. Claus, *Sci. Prog.*, 2001, **84**, 311.

51 X. Q. Qi, M. R. Axet, K. Philippot, P. Lecanted and P. Serpa, *Dalton Trans.*, 2014, **43**, 9283.

52 F. Delbecq and P. Sautet, *J. Catal.*, 1995, **152**, 217.

53 J. C. de Jesus and F. Zaera, *J. Mol. Catal. A: Chem.*, 1999, **138**, 237.

54 M. Englisch, V. S. Ranade and J. A. Lercher, *J. Mol. Catal. A: Chem.*, 1997, **121**, 69.

55 X.-C. Xiao, W. Shi, Z.-M. Ni, L.-Y. Zhang and J.-F. Xu, *Acta Phys.-Chim. Sin.*, 2015, **31**, 885.

56 B. Eveline, P. Roel and J. A. van Bokhoven, *Catal. Commun.*, 2007, **8**, 1397.

57 J. W. Medlin, *ACS Catal.*, 2011, **1**, 1284.

58 P. Claus, *Top. Catal.*, 1998, **5**, 51.

59 H. P. Rong, Z. Q. Niu, Y. F. Zhao, H. Cheng, Z. Li, L. Ma, J. Li, S. Q. Wei and Y. D. Li, *Chem. – Eur. J.*, 2015, **21**, 12034.