

CrossMark
click for updatesCite this: *Chem. Sci.*, 2015, 6, 326

Hyperbranched polydendrons: a new nanomaterials platform with tuneable permeation through model gut epithelium†

Fiona L. Hatton,^a Lee M. Tatham,^b Louise R. Tidbury,^b Pierre Chambon,^a Tao He,^c Andrew Owen^{*b} and Steven P. Rannard^{*a}

The development of nanomaterials for advanced therapies requires the formation of versatile platforms that may be tuned to maximize beneficial attributes and minimize unwanted negative behaviour. Additionally, the optimum route of administration is a key consideration of any new treatment and much work has been focused on direct injection into the systemic circulation rather than oral delivery. Here we describe a new approach to polymeric nanoparticle design and present initial results showing the potential for tuneable permeation through a gut epithelium model. Through the use of mixed initiators and branched vinyl polymerization, a series of systematically varying branched polymers have been synthesized and nanoprecipitated. The surprisingly uniform structures have undergone preliminary pharmacological evaluation to establish low cytotoxicity and enhanced permeation through model intestinal epithelial cells. This presents potential opportunities for future developments that may allow oral dosing to result in circulating polymeric nanoparticles; behaviour that may prove clinically desirable to many non-terminal or chronic diseases that utilise nanomedicines but wish to avoid regular or repeated intravenous administration.

Received 19th September 2014
Accepted 3rd October 2014

DOI: 10.1039/c4sc02889a

www.rsc.org/chemicalscience

Introduction

Clinically successful nanomedicines predominantly utilize two general approaches: orally-dosed solid-drug nanoparticles (SDNs)^{1–3} and intravenous drug-nanocarriers.^{4–6} Oral dosing is globally the most patient-acceptable drug administration format, often requiring no intervention by trained healthcare workers, offering reduced costs and requiring lower levels of sterility.^{7,8} SDN strategies aim predominantly to enhance the low oral bioavailability observed with many drug classes which may force large clinically administered doses or lead to the potential failure of new drug candidates. Relatively recently, SDNs have also been clinically evaluated as depot injections to provide long-term (months) exposure from a single subcutaneous or intramuscular injection of particulate drugs.^{9–11} Injected drug-nanocarriers (sometimes described as drug delivery systems) are typically administered intravenously and offer enhanced systemic circulation, lower doses, reduction of

side effects, and targeting/accumulation within cellular or tissue sites. Such benefits from many nanocarriers require the nanocarrier/drug vehicle to reach the systemic circulation¹² as an intact nanoparticle whereas overcoming low bioavailability *via* SDNs may result solely from enhanced drug dissolution prior to, or during, permeation of the intestinal epithelium.¹ Injections are not widely used clinically for chronic or non-terminal diseases and a clear, yet highly challenging, target for nanomedicine is the development of orally-dosed nanocarriers that can deliver drugs into the systemic circulation whilst maintaining their particulate form. Candidates such as polymeric micelles, polymer-drug conjugates, nanoprecipitates and nanoemulsions are undergoing considerable study in this respect,^{13–16} however, the synthetic/biological challenge and difficulties of *in vivo* detection within the blood, and during clearance, continue to act as a barrier to translation.

Arguably the most diverse organic nanomaterial studies have involved ideally-branched dendrimers,^{17–19} and linear-dendritic polymer hybrids.²⁰ Multi-step convergent or divergent dendrimer syntheses have led to branched polymer chemistries, from polyimines/polyamines²¹ and polycarbonates²² through to polyamides,^{23,24} polyamido-amines,²⁵ polyesters,²⁶ polyurethanes,²⁷ and polycarbosilanes²⁸ to name a selection, and dendritic polymer application²⁹ has begun to mature in nanomedicine.³⁰ Obstacles continue to exist for cost-effective applications including the synthetic complexity and molecular weight/physical size limitations. Although dendrimers possess

^aDepartment of Chemistry, University of Liverpool, Crown Street, L69 7ZD, UK. E-mail: srannard@liv.ac.uk

^bDepartment of Molecular and Clinical Pharmacology, University of Liverpool, Block H, 70 Pembroke Place, Liverpool L69 3GF, UK

^cInstitute of Chemical and Engineering Sciences, Agency for Science, Technology and Research (A*STAR), 1, Pesek Road, Jurong Island, 627833, Singapore

† Electronic supplementary information (ESI) available: Materials, full experimental details and characterisation. See DOI: 10.1039/c4sc02889a



uniform molecular weight distributions and well defined shape, the available size range has long been limited to $<15\text{ nm}^{31}$ until very recent reports of generation 13 triazine-derived materials with molecular weights $>8 \times 10^6\text{ g mol}^{-1}$ and diameters of 30 nm^{32} .

Many dendrimer materials also require lengthy syntheses that often utilize large reagent excesses. To provide broader materials options, dendrimer sub-units (dendrons) have been attached to linear polymer chain-ends or side-chains to form linear-dendritic hybrid block copolymers with multiple additional functionality and supramolecular assembly properties.²⁰ Micellar structures of amphiphilic linear-dendritic copolymers ($30\text{--}70\text{ nm}$),²⁶ and micelle aggregates (approx. 200 nm),³³ have been reported after association of relatively small building blocks. The control of structures within the $30\text{--}250\text{ nm}$ size range is of interest in drug delivery (conjugated or encapsulated drug),¹⁹ with success reported for combinations of dendrons with linear polymers leading to greater flexibility and scope for molecular design and the direction of particle formation.

One-pot, branched vinyl copolymerization techniques³⁴ have been shown to form nanoparticles in a single synthetic procedure³⁵ *via* a concerted propagation and interchain branching of linear polymer chains using low concentrations of bifunctional monomers. When used in conjunction with controlled radical polymerization techniques, high molecular weight branched amphiphilic block copolymers have been formed that produce spherical nanoparticles when dialysed using water.³⁶ The introduction of multi-functional initiators have also allowed dumbbell and clover-leaf nanoparticles to be formed,³⁷ however, the loss of chain end functional multiplicity distances these materials from ideal dendrimers or linear-dendritic hybrids.

Herein we combine the aspects of linear-dendritic hybrids and branched vinyl polymerization to provide high molecular weight dendron-functional macromolecules, termed hyper-branched-polydendrons (hyp-polydendrons).³⁸ By utilizing mixed initiator systems, this new synthetic strategy allows a ready methodology to systematically control mixed surface functionality and form complex spherical nanoparticles. These materials have: (1) a unique control of surface functionality; (2) directed aqueous self-assembly; (3) low dispersity when used to form nanoparticles with controlled diameters ($75\text{--}210\text{ nm}$); (4) encapsulation capabilities; and (5) variable interaction with model gut epithelial monolayers. Our preliminary studies of interactions of hyp-polydendron nanoprecipitates with a gut epithelium model show potential value in further work to understand and optimize nanoparticle transport across the gut barrier and the benefits that might be achievable after oral dosing.

Results and discussion

Synthesis of hyp-polydendrons with mixed functionality

To collectively overcome the synthetic complexity of dendrimer synthesis, and readily provide materials with the functional benefits of dendrimers, we recently reported the use of a dendron-derived initiator, **1**, in the copper catalysed, branched vinyl

atom transfer radical (ATRP) copolymerization of 2-hydroxypropyl methacrylate (HPMA), **2**, and ethylene glycol dimethacrylate (EGDMA), **3**, to form novel polymer architectures containing large numbers of dendrons at one end of each conjoined primary polymer chain³⁸ (Fig. 1A). We have termed these materials hyp-polydendrons as they combine a highly branched vinyl polymer core with dendron-derived chain ends

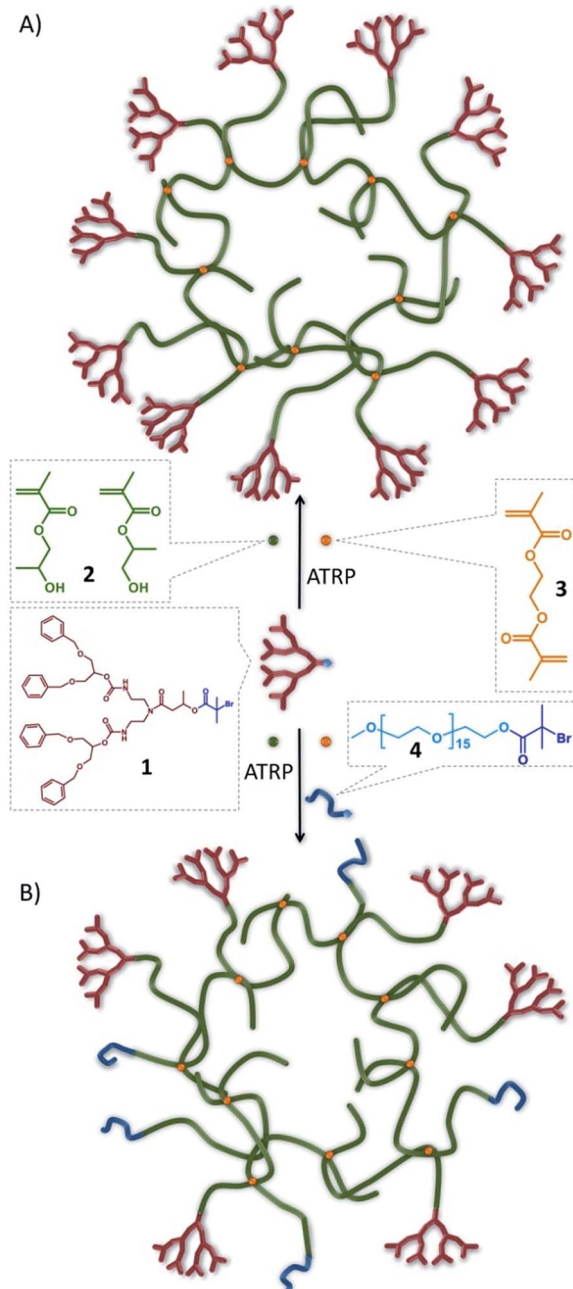


Fig. 1 Schematic representation of idealised hyp-polydendron synthesis. Atom transfer radical copolymerization (ATRP) of 2-hydroxypropyl methacrylate, **2**, and ethylene glycol dimethacrylate, **3**, initiated by the functional G₂ dendron, **1** to form (A) hyp-polydendrons; and (B) inclusion of a PEG₁₆-initiator, **4**, to form hyp-polydendrons with controlled and mixed surface functionality.



to form new hyperbranched linear-dendritic hybrid architectures.

In the absence of **3**, dendron-initiated methanolic ATRP polymerizations of **2** (target number average degree of polymerization $DP_n = 50$ monomer units), using the second generation (G_2) dendron initiator, **1**, led to high monomer conversion (>99%) and recovered polymers with a number average molecular weight (M_n) of 12 200 g mol⁻¹ and weight average molecular weight (M_w) of 16 600 g mol⁻¹, as determined by triple detection size exclusion chromatography (SEC; Table 1; Fig. S1 & S2†). In the presence of **3** (**1** : **3** molar ratio of 1 : 0.8), polymerizations also reached high conversion (>99%) with no observable interference of the controlled radical polymerization kinetics (Fig. S3†), but polymers of considerably higher molecular weight ($M_n = 90\,500$ g mol⁻¹; $M_w = 1\,304\,000$ g mol⁻¹) were recovered (Table 1).

Dendrimers with statistically mixed (divergent synthesis) and controlled mixing (convergent synthesis) of surface functionality have been reported previously.^{39–44} The hyp-polydendron synthesis strategy offers a unique opportunity for systematic incorporation of mixed functionalities through the mixing of ATRP initiators. Dendron-derived initiators guarantee one dendron on each primary polymer chain, but the introduction of varying ratios of a polyethylene glycol-derived (PEG₁₆) ATRP initiator, **4**, to **1** prior to copolymerization of **2** and **3** (Fig. 1B) has been undertaken. A range of branched polymerizations were conducted with **1** : **4** ratios of 100 : 0, 90 : 10, 75 : 25, 50 : 50, 25 : 75, 10 : 90 and 0 : 100, whilst maintaining the overall initiating species (based on tertiary bromide functionality) to brancher, (**1** + **4**) : **3**, ratio of 1 : 0.8. Polymerization kinetic studies confirmed controlled radical polymerization, however, the achieved molecular weights (M_n and M_w) decreased with increasing content of **4**. This is quite possibly due to an overall increase in initiation efficiency generating a decrease in the effective initiator : brancher ratio and subsequent lower branching; M_w values ranging between 1 495 000–296 000 g mol⁻¹ were observed across the range of initiator

mixtures when utilising a (**1** + **4**) : **3** molar ratio of 1 : 0.8 (Table 1; Fig. S2†). Increased levels of **3** were tolerated within the polymerizations containing high concentrations of, **4** without the presence of gelation and M_w values between 2-fold and 4-fold higher were achievable at (**1** + **4**) : **3** molar ratio of 1 : 0.95 (Table 1); M_n values were also considerably increased.

Confirmation of the varying **1** : **4** ratio within the various hyp-polydendron structures was obtained by ¹H nuclear magnetic resonance (NMR) spectroscopy (Fig. S4†). The calculated molar variation of G_2 dendron and PEG₁₆ end-groups were observed to follow theoretical concentrations closely (Fig. S5†); however, at higher target G_2 dendron values, slightly lower dendron incorporation was observed, again a potential effect of the differing initiator efficiencies.

Aqueous nanoprecipitation and characterisation of hyp-polydendrons with mixed surface functionality

Nanoprecipitation of linear polymers⁴⁵ has previously generated uniform spherical nanoparticles predominantly from biodegradable polymers.⁴⁶ The nanoprecipitation mechanism is proposed to undergo a nucleation/aggregation process⁴⁷ and a multitude of factors may be varied (solvent choice, polymer concentration, viscosity) to direct the formation of colloidal stable particles of varying size.⁴⁸ We recently demonstrated the successful aqueous nanoprecipitation of branched polymer architectures⁴⁹ and the self-assembly of hyp-polydendrons³⁸ within organic solvent mixtures and water to form uniform, spherical, self-assembled nanostructures.

Successful nanocarrier candidates (100–200 nm), formed by careful control of polymer structure and nanoprecipitation,^{50,51} have previously shown the potential for relatively high drug loadings. Chain-end modification of polyethylene glycol segments within amphiphilic A–B block copolymers by aptamers (Accurin™ technology) has also led to positive phase I evaluation of drug delivery to sites of prostate and lung cancer^{51,52} from injected nanoprecipitates with recently

Table 1 SEC characterisation of polydendrons produced using varying G_2 dendron-PEG₁₆ initiator ratios and under varying polymerization conditions

| Initiator (mol fraction) | | Target polymer composition | SEC | | |
|--------------------------|-------------------|--|---------|-----------|---------------|
| G_2 | PEG ₁₆ | | M_n | M_w | $D (M_w/M_n)$ |
| 1 | 0 | HPMA ₅₀ ^a | 12 200 | 16 600 | 1.36 |
| 0.5 | 0.5 | HPMA ₅₀ ^a | 13 000 | 16 900 | 1.30 |
| 0 | 1 | HPMA ₅₀ ^a | 10 600 | 16 800 | 1.59 |
| 1 | 0 | HPMA ₅₀ -EGDMA _{0.8} ^b | 90 500 | 1 304 000 | 14.40 |
| 0.9 | 0.1 | HPMA ₅₀ -EGDMA _{0.8} ^b | 68 500 | 1 495 000 | 21.84 |
| 0.75 | 0.25 | HPMA ₅₀ -EGDMA _{0.8} ^b | 52 400 | 987 800 | 18.88 |
| 0.5 | 0.5 | HPMA ₅₀ -EGDMA _{0.8} ^b | 39 400 | 480 700 | 12.19 |
| 0.25 | 0.75 | HPMA ₅₀ -EGDMA _{0.8} ^b | 36 200 | 315 300 | 8.73 |
| 0.1 | 0.9 | HPMA ₅₀ -EGDMA _{0.8} ^b | 37 700 | 286 000 | 7.61 |
| 0 | 1 | HPMA ₅₀ -EGDMA _{0.8} ^b | 68 100 | 296 200 | 4.35 |
| 0.5 | 0.5 | HPMA ₅₀ -EGDMA _{0.95} ^c | 121 900 | 1 779 000 | 14.60 |
| 0 | 1 | HPMA ₅₀ -EGDMA _{0.95} ^c | 74 700 | 642 700 | 8.60 |

^a Linear polymerization. ^b Branched polymerizations at total initiator : brancher ratio = 1 : 0.8. ^c Branched polymerizations at total initiator : brancher ratio = 1 : 0.95.





Fig. 2 Nanoprecipitation of hyp-polydendrons. (A) Schematic of nano-precipitation from THF (good solvent) into water (poor solvent). Dissolved and expanded hyp-polydendrons collapse, forming self-assembling nuclei that form stable nanoparticles aqueous environments; (B) schematic representation of hyp-polydendron nanoprecipitates containing (i) 100% dendron initiator, (ii) a 50 : 50 molar ratio of G₂ dendron-PEG₁₆ initiators, and (iii) 100% PEG₁₆ initiator; (C) scanning electron microscopy images of hyp-polydendron nanoprecipitates (initial concentration in THF = 5 mg mL⁻¹, final aqueous concentration = 1 mg mL⁻¹) with varying G₂ dendron-PEG₁₆ molar ratios: (i) 100 : 0, (ii) 90 : 10, (iii) 50 : 50, and (iv) 25 : 75; (D) atomic force microscopy of hyp-polydendron nanoprecipitate particles (initial concentration in THF = 5 mg mL⁻¹, final aqueous concentration = 1 mg mL⁻¹): (i) size image for nanoprecipitates generated from a G₂ dendron-PEG₁₆ molar ratio of 100 : 0, (ii) contour image of nanoprecipitates with a G₂ dendron-PEG₁₆ molar ratio of 25 : 75.

of the nanoparticles without dissolution, even at high levels of THF (>37.5% v/v) (Fig. S7b†), whilst dilution of the nanoparticles with water led to no appreciable changes over considerable concentration ranges (Fig. S7a†).

Conversely, studies of nanoprecipitates derived from the analogous unbranched linear-dendritic hybrids that comprise the primary chain structure of the hyp-polydendrons, and PEG₁₆-(HPMA)₅₀ analogues (Table 1), led to broad size distributions after nanoprecipitation and increasing *D_z* and PDI (bimodal size distributions in some cases) over extended periods, with visual precipitation (Fig. S8†).

Nile Red (NR) and pyrene encapsulation was accomplished by co-dissolving the fluorescent dyes into the branched polymer-THF solution of (0.1% w/w relative to polymer) prior to nanoprecipitation. These dyes were chosen due to their environment-dependent fluorescence and the ability to report on differences in lipophilicity (NR) or polarity (pyrene) within the core of the nanoprecipitates; no appreciable changes to *D_z* (Fig. S9 and S10†) were observed with encapsulated dye. NR emission (630 nm) was measured after excitation at 552 nm and was clearly dependent on the G₂ dendron-PEG₁₆ ratio (Fig. 3A).

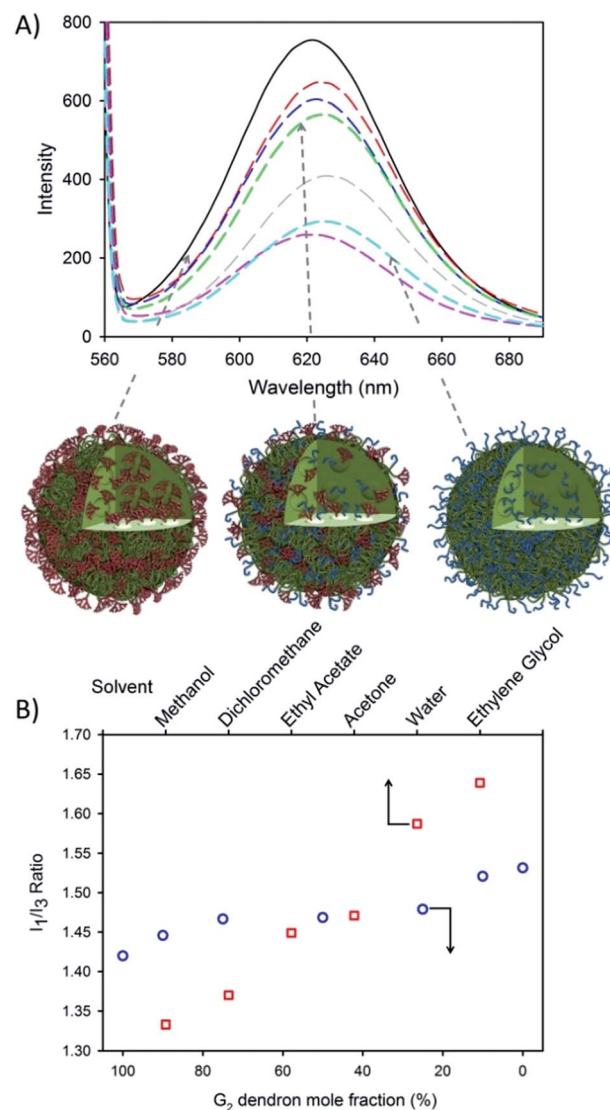


Fig. 3 Encapsulation of hydrophobic guest molecules during nanoprecipitation of hyp-polydendrons with varying G₂ dendron-PEG₁₆ content. (A) Fluorimetric analysis of hyp-polydendron nanoprecipitates containing Nile Red produced from varying G₂ dendron-PEG₁₆ initiator ratios of 100 : 0 (solid black), 90 : 10 (red dash), 75 : 25 (blue dash), 50 : 50 (green dash), 27 : 75 (pink dash), 10 : 90 (grey dash) and 0 : 100 (cyan dash); (B) comparison of the observed I₁/I₃ ratio of pyrene within varying solvents (open red squares)^{53,54} and encapsulated within hyp-polydendrons synthesized using different G₂ dendron-PEG₁₆ initiator ratios (open blue circles).



This suggests the control of the environment within the hyp-polydendron nanoprecipitates whilst simultaneously modifying the expression of surface functionality. This is consistent with an assembly model involving aggregation of individual collapsed hyp-polydendron nuclei as complete entrapment of hyp-polydendrons within the nanoprecipitate would result (Fig. 3A), leading to internalization of varying internal ratios of G₂ dendron and PEG₁₆.

Further investigation of the internal nanoparticle environment was conducted *via* pyrene encapsulation. A similar variation of the internal nanoparticle environment was observed within the fine structure of pyrene fluorescence after excitation at 335 nm (Fig. S11†). The ratio of the intensities of the first and third vibrational bands (I_1/I_3) varied from 1.42–1.53, similar to pyrene fluorescence observed in solvents with polarities ranging from dichloromethane ($I_1/I_3 = 1.37$) to water ($I_1/I_3 = 1.59$) (Fig. 3B).^{53,54} The observed modification of the nanoparticle internal environment allows the potential for tuning of nanoparticle properties *via* initiator chemistry and/or monomer choice, providing considerable scope for tuning of physical properties. Similarly, modification of surface chemistry of the nanoprecipitate may also alter cellular or tissue interactions and this was investigated further with respect to model gut epithelium.

Model epithelial permeation studies using aqueous hyp-polydendron nanoprecipitates

There are many clinically-utilized nanocarrier therapies benefiting patients globally, across diseases including cancer (*e.g.* Doxil and Myocet), fungal infection (*e.g.* Abelcet and AmBisome), hepatitis (*e.g.* Epaxal and Pegintron) and meningitis (*e.g.* DepoCyt).⁵⁵ Dendrimers have been utilized as DNA transfection reagents (*e.g.* SuperFECT) and cancer/cardiac diagnostics (Stratus CS Acute Care Assay), whilst only limited dendrimer-derived therapeutics are being sought (*e.g.* VivaGel®).⁵⁵

Nanocarriers are rarely dosed orally,⁵⁶ but benefits may accrue in chronic diseases (*e.g.* HIV therapy or psychiatric disorders) where long-term daily dosing is required and repeated injection is not optimal for patients. The provision of an orally-administered nanocarrier, delivering nanoparticles to the circulation, may also provide cellular or tissue targeting benefits for acute diseases. Our aim within this study was to evaluate the potential for permeation through a gut epithelium model; therefore, a preliminary *in vitro* pharmacological evaluation of the behaviour of hyp-polydendron nanoprecipitates was conducted.

Cytotoxicity of the seven aqueous nanoprecipitates was evaluated against the human epithelial colorectal adenocarcinoma (Caco-2) cell line (Fig. 4A) and no appreciable cytotoxicity was observed at achievable concentrations in assays assessing either adenosine triphosphate or 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyltetrazolium bromide (MTT) turnover (Fig. S12a–d†); as such the determination of an IC₅₀ value for each polymer was not possible, indicating very low cytotoxicity towards Caco-2 cells. In the absence of obvious cytotoxicity to the gut model cell

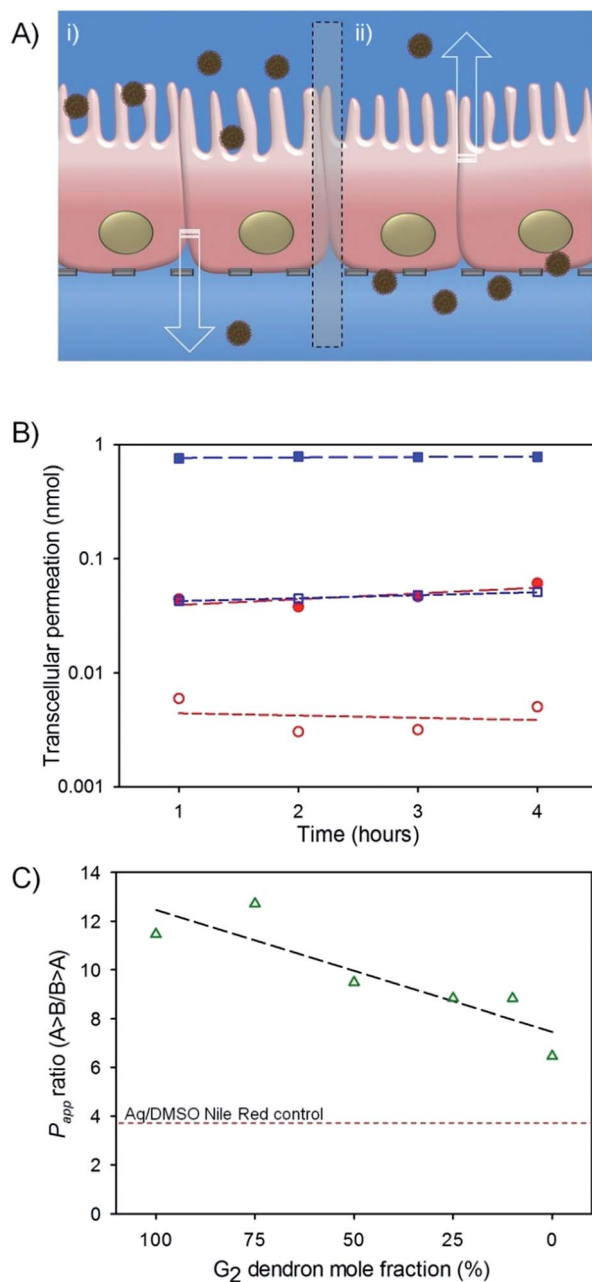


Fig. 4 Preliminary evaluation of oral dosing potential for hyp-polydendron nanoprecipitates with varying G₂ dendron–PEG₁₆ content. (A) Schematic representation of hyp-polydendron nanoprecipitates passing from (i) apical (top) compartment (modelling the gut side) of a differentiated Caco-2 cell monolayer through to the basolateral (bottom) compartment (modelling the blood side) to evaluate potential for intestinal epithelium permeation, and (ii) movement of hyp-polydendron nanoprecipitates from the basolateral to the apical side of the monolayer; (B) comparison of permeation of a hyp-polydendron (10 : 90 G₂ dendron–PEG₁₆ ratio) nanoprecipitate (blue squares) and aqueous/DMSO solution (<1% v/v) of Nile Red (red circles) through a Caco-2 monolayer – B > A permeation (open symbols); A > B permeation (closed symbols) (C) apparent permeability (P_{app}) of Nile Red when encapsulated in hyp-polydendron nanoprecipitates of varying G₂ dendron–PEG₁₆ molar ratios (open green triangles) and as an aqueous/DMSO solution (<1% v/v) (red line).



- 5 R. Duncan, *Curr. Opin. Biotechnol.*, 2011, **22**, 492–501.
- 6 C. E. Ashley, E. C. Carnes, G. K. Phillips, D. Padilla, P. N. Durfee, P. A. Brown, T. N. Hanna, J. Liu, B. Phillips, M. B. Carter, N. J. Carroll, X. Jiang, D. R. Dunphy, C. L. Willman, D. N. Petsev, D. G. Evans, A. N. Parikh, B. Chackerian, W. Wharton, D. S. Peabody and C. J. Brinker, *Nat. Mater.*, 2011, **10**, 389–397.
- 7 F. E. Stuurman, B. Nuijen, J. H. Beijnen and J. H. M. Schellens, *Clin. Pharmacokinet.*, 2013, **52**, 399–414.
- 8 M. D. N. Siddiqui, G. Garg and P. K. Sharma, *Adv. Biol. Res.*, 2011, **5**, 291–303.
- 9 (a) M. Boffito, A. Jackson, A. Owen and S. Becker, *Drugs*, 2014, **74**, 7–13; (b) M. N. Samtani, A. Vermeulen and K. Stuyckens, *Clin. Pharmacokinet.*, 2009, **48**, 585–600.
- 10 G. van't Klooster, E. Hoeben, H. Borghys, A. Loosova, M.-P. Bouche, F. van Velsen and L. Baert, *Antimicrob. Agents Chemother.*, 2010, **54**, 2042–2050.
- 11 W. Spreen, S. Min, S. L. Ford, S. Chen, Y. Lou, M. Bomar, M. St Clair, S. Piscitelli and T. Fujiwara, *HIV Clin. Trials*, 2013, **14**, 192–203.
- 12 M. C. Branco and J. P. Schneider, *Acta Biomater.*, 2009, **5**, 817–831.
- 13 G. Gaucher, P. Satturwar, M.-C. Jones, A. Furtos and J.-C. Leroux, *Eur. J. Pharm. Biopharm.*, 2010, **76**, 147–158.
- 14 L. Bromberg, *J. Controlled Release*, 2008, **128**, 99–112.
- 15 I. Pepić, J. Lovrić and J. Filipović-Grčić, *Eur. J. Pharm. Sci.*, 2013, **50**, 42–55.
- 16 L. Mei, Z. Zhang, L. Zhao, L. Huang, X.-L. Yang, J. Tang and S.-S. Feng, *Adv. Drug Delivery Rev.*, 2013, **65**, 880–890.
- 17 S. M. Grayson and J. M. J. Fréchet, *Chem. Rev.*, 2001, **101**, 3819–3867.
- 18 L. Röglin, E. H. M. Lempens and E. W. Meijer, *Angew. Chem., Int. Ed.*, 2011, **50**, 102–112.
- 19 C. C. Lee, J. A. MacKay, J. M. J. Fréchet and F. Szoka, *Nat. Biotechnol.*, 2005, **23**, 1517–1526.
- 20 F. Wurm and H. Frey, *Prog. Polym. Sci.*, 2011, **36**, 1–52.
- 21 T. M. Hermans, M. A. C. Broeren, N. Gomopoulos, P. van der Schoot, M. H. P. van Genderen, N. A. J. M. Sommerdijk, G. Fytas and E. W. Meijer, *Nat. Nanotechnol.*, 2009, **4**, 721–726.
- 22 S. P. Rannard and N. J. Davis, *J. Am. Chem. Soc.*, 2000, **122**, 11729–11730.
- 23 S. Rannard, N. Davis and H. McFarland, *Polym. Int.*, 2000, **49**, 1002–1006.
- 24 F. Aulenta, M. G. B. Drew, A. Foster, W. Hayes, S. Rannard, D. W. Thornthwaite, D. R. Worrall and T. G. A. Youngs, *J. Org. Chem.*, 2005, **70**, 63–78.
- 25 M. S. Diallo, L. Balogh, A. Shafagati, J. H. Johnson, W. A. Goddard and D. A. Tomalia, *Environ. Sci. Technol.*, 1999, **33**, 820–824.
- 26 A. Carlmark, E. Malmström and M. Malkoch, *Chem. Soc. Rev.*, 2013, **42**, 5858–5879.
- 27 A. Stoddart, W. J. Feast and S. P. Rannard, *Soft Matter*, 2012, **8**, 1096–1108.
- 28 P. Ortega, M. J. Serramia, M. A. Munoz-Fernandez, F. J. de la Mata and R. Gomez, *Tetrahedron*, 2010, **66**, 3326–3331.
- 29 D. Astruc, E. Boisselier and C. Ornelas, *Chem. Rev.*, 2010, **110**, 1857–1959.
- 30 J. M. Oliveira, A. J. Salgado, N. Sousa, J. F. Mano and R. L. Reis, *Prog. Polym. Sci.*, 2010, **35**, 1163–1194.
- 31 A. R. Menjoge, R. M. Kannan and D. A. Tomalia, *Drug Discovery Today*, 2010, **15**, 171–185.
- 32 J. Lim, M. Kostiainen, J. Maly, V. C. P. da Costa, O. Annunziata, G. M. Pavan and E. E. Simanek, *J. Am. Chem. Soc.*, 2013, **135**, 4660–4663.
- 33 Y. Chang and C. Kim, *J. Polym. Sci., Part A-1: Polym. Chem.*, 2001, **39**, 918–926.
- 34 N. O'Brien, A. McKee, D. C. Sherrington, A. T. Slark and A. Titterton, *Polymer*, 2000, **41**, 6027–6031.
- 35 J. V. M. Weaver, S. P. Rannard and A. I. Cooper, *Angew. Chem., Int. Ed.*, 2009, **48**, 2131–2136.
- 36 T. He, D. J. Adams, M. F. Butler, C. T. Yeoh, A. I. Cooper and S. P. Rannard, *Angew. Chem., Int. Ed.*, 2007, **46**, 9243–9247.
- 37 T. He, D. J. Adams, M. F. Butler, A. I. Cooper and S. P. Rannard, *J. Am. Chem. Soc.*, 2009, **131**, 1495–1501.
- 38 F. L. Hatton, P. Chambon, T. O. McDonald, A. Owen and S. P. Rannard, *Chem. Sci.*, 2014, **5**, 1844–1853.
- 39 R. B. Kolhatkar, K. M. Kitchens, P. W. Swaan and H. Ghandehari, *Bioconjugate Chem.*, 2007, **18**, 2054–2060.
- 40 H. Willcock, A. I. Cooper, D. J. Adams and S. P. Rannard, *Chem. Commun.*, 2009, 3095–3097.
- 41 B. Huang, J. F. Kukowska-Latallo, S. Tang, H. Zong, K. B. Johnson, A. Desai, C. L. Gordon, P. R. Leroueil and J. R. Baker, *Bioorg. Med. Chem. Lett.*, 2012, **22**, 3152–3156.
- 42 C. J. Hawker and J. M. J. Fréchet, *J. Am. Chem. Soc.*, 1992, **114**, 8405–8413.
- 43 K. Yoon, P. Goyal and M. Weck, *Org. Lett.*, 2007, **9**, 2051–2054.
- 44 P. Antoni, Y. Hed, A. Nordberg, D. Nystrom, H. von Holst, A. Hult and M. Malkoch, *Angew. Chem., Int. Ed.*, 2009, **48**, 2126–2130.
- 45 O. Thioune, H. Fessi, J. P. Devissaguet and F. Puisieux, *Int. J. Pharm.*, 1997, **146**, 233–238.
- 46 S. Schubert, J. T. Delaney and U. S. Schubert, *Soft Matter*, 2011, **7**, 1581–1588.
- 47 V. K. Lamer and R. H. Dinegar, *J. Am. Chem. Soc.*, 1950, **72**, 4847–4854.
- 48 C. Zhang, V. J. Pansare, R. K. Prud'homme and R. D. Priestly, *Soft Matter*, 2012, **8**, 86–93.
- 49 R. A. Slater, T. O. McDonald, D. J. Adams, E. R. Draper, J. V. M. Weaver and S. P. Rannard, *Soft Matter*, 2012, **8**, 9816–9827.
- 50 P. M. Valencia, P. A. Basto, L. Zhang, M. Rhee, R. Langer, O. C. Farokhzad and R. Karnik, *ACS Nano*, 2010, **4**, 1671–1679.
- 51 J. Cheng, B. A. Teply, I. Sherifi, J. Sung, G. Luther, F. X. Gu, E. Levy-Nissenbaum, A. F. Radovic-Moreno, R. Langer and O. C. Farokhzad, *Biomaterials*, 2007, **28**, 869–876.
- 52 J. Shi, Z. Xiao, N. Kamaly and O. C. Farokhzad, *Acc. Chem. Res.*, 2011, **44**, 1123–1134.
- 53 D. C. Dong and M. A. Winnik, *Photochem. Photobiol.*, 1982, **35**, 17–21.



- 54 K. Kalyanasundaram and J. K. Thomas, *J. Am. Chem. Soc.*, 1977, **99**, 2039–2044.
- 55 R. Duncan and R. Gaspar, *Mol. Pharm.*, 2011, **8**, 2101–2141.
- 56 S. Maher, T. W. Leonard, J. Jacobsen and D. J. Brayden, *Adv. Drug Delivery Rev.*, 2009, **61**, 1427–1449.
- 57 L. Profit, V. A. Eagling and D. J. Back, *AIDS*, 1999, **13**, 1623–1627.
- 58 P. Palumbo, U. Picchini, B. Beck, J. van Gelder, N. Delbar and A. DeGaetano, *J. Pharmacokinet. Pharmacodyn.*, 2008, **35**, 235–248.

