



CrossMark
click for updates

Cite this: *Environ. Sci.: Nano*, 2016, 3, 190

Effects of crystallite size on the structure and magnetism of ferrihydrite†

Xiaoming Wang,^{ab} Mengqiang Zhu,^b Luuk K. Koopal,^c Wei Li,^d Wenqian Xu,^e Fan Liu,^a Jing Zhang,^f Qingsong Liu,^{gh} Xionghan Feng^{*a} and Donald L. Sparksⁱ

The structure and magnetic properties of nano-sized (1.6 to 4.4 nm) ferrihydrite samples are systematically investigated through a combination of X-ray diffraction (XRD), X-ray pair distribution function (PDF), X-ray absorption spectroscopy (XAS) and magnetic analyses. The XRD, PDF and Fe K-edge XAS data of the ferrihydrite samples are all fitted well with the Michel ferrihydrite model, indicating similar local-, medium- and long-range ordered structures. PDF and XAS fitting results indicate that, with increasing crystallite size, the average coordination numbers of Fe–Fe and the unit cell parameter *c* increase, while Fe2 and Fe3 vacancies and the unit cell parameter *a* decrease. Mössbauer results indicate that the surface layer is relatively disordered, which might have been caused by the random distribution of Fe vacancies. These results support Hiemstra's surface-depletion model in terms of the location of disorder and the variations of Fe2 and Fe3 occupancies with size. Magnetic data indicate that the ferrihydrite samples show antiferromagnetism superimposed with a ferromagnetic-like moment at lower temperatures (100 K and 10 K), but ferrihydrite is paramagnetic at room temperature. In addition, both the magnetization and coercivity decrease with increasing ferrihydrite crystallite size due to strong surface effects in fine-grained ferrihydrites. Smaller ferrihydrite samples show less magnetic hyperfine splitting and a lower unblocking temperature (T_B) than larger samples. The dependence of magnetic properties on grain size for nano-sized ferrihydrite provides a practical way to determine the crystallite size of ferrihydrite quantitatively in natural environments or artificial systems.

Received 2nd September 2015,
Accepted 12th December 2015

DOI: 10.1039/c5en00191a

rsc.li/es-nano

Nano impact

Despite numerous studies, the surface structure and magnetism of ferrihydrite are still not clearly understood. In this study, ferrihydrite samples with different crystallite sizes were found to share similar short-, medium- and long-range structures, but with decreasing size, the Fe–Fe coordination numbers decreased and the surface layer disorder increased. An investigation of the magnetization indicated that magnetization decreases with increasing size. Smaller samples exhibit lower magnetic-order temperature and unblocking temperatures. In contrast, for ordered, relatively large ferrihydrites, magnetic enhancement with size was found. It is therefore predicted that the change in magnetization with size likely has a minimum. The present structure and magnetization results significantly contribute to the understanding of the ferrihydrite structure, its surface reactivity and its magnetic behavior in the environment.

^a Key Laboratory of Arable Land Conservation (Middle and Lower Reaches of Yangtze River), Ministry of Agriculture, College of Resources and Environment, Huazhong Agricultural University, Wuhan 430070, China.

E-mail: fch73@mail.hzau.edu.cn; Fax: +86 27 87288618; Tel: +86 27 87280271

^b Department of Ecosystem Science and Management, University of Wyoming, Laramie, WY, 82071, USA

^c Physical Chemistry and Soft Matter, Wageningen University, Dreijenplein 6, 6703 HB Wageningen, Netherlands

^d Key Laboratory of Surficial Geochemistry, Ministry of Education, School of Earth Sciences and Engineering, Nanjing University, Nanjing 210093, China

^e Department of Chemistry, Brookhaven National Lab, Upton, New York 11973, USA

^f Beijing Synchrotron Radiation Facility, Institute of High Energy Physics, Chinese Academy of Sciences, Beijing 100039, China

^g State Key Laboratory of Lithospheric Evolution, Institute of Geology and Geophysics, Chinese Academy of Sciences, Beijing 100029, China

^h Function Laboratory for Marine Geology, National Oceanography Laboratory, Qingdao 266061, China

ⁱ Environmental Soil Chemistry Group, Delaware Environmental Institute and Department of Plant and Soil Sciences, University of Delaware, Newark, Delaware, 19716, USA

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c5en00191a





Fig. 1 XRD patterns of the four ferrihydrite samples (blue lines), Rietveld fitting results (red solid lines), and difference between the experimental data and the fit (black solid lines below the data). R_{wp} is the goodness of fit.

10 K to obtain the FC magnetization curves. The measurement step was set to 5 K.

Results

Structure of ferrihydrite

X-ray diffraction. The powder XRD patterns of the ferrihydrite samples (blue lines) are shown in Fig. 1. In decreasing order, the d -spacing values of the characteristic peaks and the corresponding diffraction indices (hkl) of 6LFh are as follows: 2.50 Å (110), 2.21 Å (200), 1.96 Å (113), 1.72 Å (114), 1.51 Å (115) and 1.48 Å (106) (JCPDS No. 29-0712). Poorly crystalline 2LFh_1 has two broad peaks with d -spacing (2θ) values of 2.50 Å (35.8°) and 1.51 Å (62.7°). The 5LFh_2 and 5LFh_3 samples show 5 peaks (lines) at d -spacing values (2θ) of 2.50 Å (35.8°), 2.21 Å (40.7°), 1.96 Å (46.3°), 1.72 Å (53.2°) and 1.51 Å (61.9°). The 6LFh_4 sample shows six peaks (lines); in addition to the five peaks mentioned above, it shows a shoulder peak with a d -spacing value of 1.48 Å (63.4°). The above analysis indicates that the samples vary from two-line ferrihydrite to six-line ferrihydrite. In addition, from 2LFh_1 to 6LFh_4, the full width at half maximum (FWHM) of the peaks gradually decreases, which implies that the crystallite size gradually increases.

The results of fitting of the XRD data for the studied ferrihydrites (red lines) using the Rietveld method are shown in Fig. 1 and Table SI-1.† Small differences between the observed and fitted patterns (grey lines) indicate that the XRD data can be fitted well with the Michel model,²¹ implying that the long-range bulk structures of 2LFh_1 to 6LFh_4 are very similar. The excellent fitting indicates that the obtained crystallite sizes are reasonable; they amount to 1.6, 2.6, 3.4 and 4.4 nm respectively for 2LFh_1, 5LFh_2, 5LFh_3 and 6LFh_4,



Fig. 2 Pair distribution functions [$G(r)$ functions] of the four synthetic ferrihydrite samples. Panel (a) shows the experimental results in the r range of 0–50 Å. In panel (b), the experimental (black blank squares) and calculated (red solid lines) PDFs for the ferrihydrite samples are compared in the r range of 1–20 Å; the grey curves are the differences and R_w indicates the goodness of fit. Panel (c) shows the deconvolution of the total $G(r)$ of 2LFh_1 in its calculated major atomic correlations. The numbers indicate the most important peak positions.

i.e., the crystallite size increases from 2LFh_1 to 6LFh_4. However, the obtained unit cell parameters (Table SI-1†) are



likely not entirely realistic, because there was no strict restriction for the atomic positions and other structural factors during fitting with the present method. More reliable values have been obtained by PDF analysis.

Pair distribution function analysis. The PDFs or $G(r)$ functions of the four ferrihydrite samples are shown in Fig. 2. A $G(r)$ reveals peaks at characteristic atom-pair distances and thus reflects the crystal structure. The four samples have similar $G(r)$ s in the r range of 0–50 Å (Fig. 2a). Due to the limited CSD size, $G(r)$ shows attenuation with increasing interatomic distance (r), and the attenuation completes as r approaches the dimensions of the scattering body.^{47,48} From 2LFh_1 to 6LFh_4, the attenuation rate decreases, and the distances over which the attenuation completes (indicated by the arrows in Fig. 2a) are approximately 2.0, 2.6, 3.4 and 4.4 nm for 2LFh_1, 5LFh_2, 5LFh_3 and 6LFh_4, respectively. These sizes generally agree with the crystallite sizes obtained through the XRD Rietveld refinement and with sizes previously obtained using transmission electron microscopy (TEM).¹³

A comparison of the $G(r)$ functions between 1 and 20 Å (Fig. 2b) reveals that all ferrihydrite samples share nearly the same atomic arrangement, *i.e.*, they have a similar medium-range structure. To quantify structural variations caused by crystallite size changes, the $G(r)$ functions were modeled against the Michel model.²¹ The R_w values indicate that the simulated $G(r)$ is in good agreement with the experimental data (Fig. 2b). The results show that (Table 1), with increasing crystallite size, the unit cell parameter a decreases, while the unit cell parameter c and Fe2 and Fe3 site occupancies all increase, broadly consistent with existing reports.^{18,21} In addition, the deconvolution of the total $G(r)$ in the calculated $G(r)$ of the Fe–O, Fe–Fe and O–O atomic pairs for 2LFh_1 is shown in Fig. 2c. The first three peaks in the $G(r)$ functions correspond to (i) the Fe–O atomic pairs in the FeO₆ octahedra with an Fe–O bond length of 1.99 Å, (ii) Fe–Fe pairs between two edge-sharing FeO₆ octahedra with an Fe–Fe distance of 3.04 Å and (iii) Fe–Fe pairs between two corner-sharing octahedra and/or tetrahedra with an Fe–Fe distance of 3.43 Å.

X-ray absorption spectroscopy. The ferrihydrite samples also have similar Fe K-edge X-ray absorption near edge structure (XANES) spectra (Fig. 3a). The shape and relative intensity of the edge jump at ~7126 eV, as well as the pre-edge peak at ~7113.5 eV, corresponding well with existing reports.^{42,49–51} The white line for ferrihydrite is located at 7132.2 eV, and the peak at 7147.6 eV is due to multiple scattering by the atoms from the first and second coordination shells.⁴²

The k space EXAFS spectra of the samples (Fig. 3b) are also similar and consistent with previous reports.^{42,52} The peak intensities at ~5, ~7.5 and ~9.5 Å (see the arrows) are representative of high-shell backscattering signals;⁵² they slightly decrease with decreasing crystallite size, suggesting a slightly reduced number of nearest Fe neighbors.

The radial structural functions (RSFs) (*i.e.*, Fourier transform) of the K-edge EXAFS are shown in Fig. 3c. The first large peak corresponds to the first nearest neighbors (O, OH or OH₂) of the absorbing Fe atoms, the second shell results from Fe–Fe edge-sharing of FeO₆ octahedra, and the third shell can be ascribed to Fe–Fe corner-sharing configurations.⁵² The similar RSFs of the ferrihydrite samples suggest that they have similar Fe local coordination environments, consistent with the PDF results (Fig. 2). However, the amplitude of the two Fe–Fe coordination peaks gradually decreases with decreasing size, which implies decreasing average coordination numbers (CNs) of neighboring Fe atoms and/or a gradually increasing degree of disorder of Fe–Fe arrangements with decreasing crystallite size.

The EXAFS spectra were fitted by including the Fe–O and Fe–Fe single-scattering paths obtained from the Michel model and the Fe–O–O multiple-scattering (MS) path. The MS path parameters were correlated as described by Mikutta.⁵⁰ The spectra and the fits are compared in Fig. 3d, and the obtained structural parameters are listed in Table 2. The results indicate that the first-shell Fe–O coordination has an average Fe–O bond length of 1.97 ± 0.01 Å for all samples with the corresponding coordination number (CN_{Fe-O}) ranging from 5.20 ± 0.18 to 5.46 ± 0.23 , in good agreement with the PDF results (Fig. 2c) and the reported XAS fitting results.^{50,52,53} The average Fe–Fe1 distance of 3.04 ± 0.01 Å and

Table 1 The structural parameters obtained from PDF fitting for the studied ferrihydrite samples. Values in brackets are fitting errors

| Parameters | Samples | | | |
|--------------------|-----------|-----------|-----------|-----------|
| | 2LFh_1 | 5LFh_2 | 5LFh_3 | 6LFh_4 |
| a (Å) | 6.017(12) | 6.010(11) | 5.991(9) | 5.995(9) |
| c (Å) | 9.074(33) | 9.122(27) | 9.142(23) | 9.227(24) |
| Fe2 and Fe3 (occ.) | 0.825(39) | 0.845(38) | 0.859(34) | 0.882(34) |
| Q_{damp} | 0.077(13) | 0.090(6) | 0.085(5) | 0.083(4) |
| δ_2 | 2.70(36) | 3.06(41) | 2.98(42) | 3.09(45) |
| Scale factor | 1.235 | 1.014 | 1.044 | 0.944 |
| Diameter (Å) | 16 | 26 | 34 | 44 |
| R_w (%) | 17.8 | 18.2 | 20.3 | 23.3 |

a and c : unit cell parameters; Fe2 and Fe3 occ.: the occupancy of Fe2 and Fe3 were set equal; Q_{damp} : damping factor; δ_2 : vibrational correlation terms; crystallite diameters: the sp-diameters of the ferrihydrite samples were fixed at the values obtained from XRD fitting; R_w values were calculated between $r_{min} = 1$ Å and $r_{max} = 20$ Å.





Fig. 3 Fe K-edge XANES (a); the k^3 -weighted EXAFS spectra, where the arrows indicate the main oscillations affected by the crystallite size (b); the Fourier transforms (magnitude) of the k^3 -weighted EXAFS spectra (c); the radial distribution functions (symbols) and their fits using the Michel model (red curves) (d).

Table 2 Fe K-edge EXAFS structural parameters derived from the fits of the spectra of the ferrihydrite samples. The amplitude reduction factor, S_0^2 , was fixed at 0.83 for all samples.⁵² Fits were performed in R -space over an R -range of 0.8–3.5 Å. The values in brackets indicate the fitting error

| Samples | Path | R^a (Å) | CNs ^b | σ^{2c} (Å ²) | ΔE_0^d (eV) | R -factor ^e (%) |
|---------|--------|-----------|------------------|---------------------------------|---------------------|------------------------------|
| 2LFh_1 | Fe–O | 1.97(1) | 5.20(18) | 0.011 | –3.4(9) | 0.8 |
| | Fe–Fe1 | 3.04(1) | 2.50(40) | 0.015 | | |
| | Fe–Fe2 | 3.44(1) | 3.71(55) | 0.015 | | |
| 5LFh_2 | Fe–O | 1.97(1) | 5.46(23) | 0.011 | –3.5(10) | 1.1 |
| | Fe–Fe1 | 3.04(1) | 2.72(51) | 0.015 | | |
| | Fe–Fe2 | 3.43(1) | 4.31(69) | 0.015 | | |
| 5LFh_3 | Fe–O | 1.97(1) | 5.44(23) | 0.011 | –3.6(10) | 1.1 |
| | Fe–Fe1 | 3.04(1) | 2.81(49) | 0.015 | | |
| | Fe–Fe2 | 3.42(1) | 4.46(66) | 0.015 | | |
| 6LFh_4 | Fe–O | 1.97(1) | 5.29(23) | 0.011 | –3.4(11) | 1.1 |
| | Fe–Fe1 | 3.04(1) | 2.84(50) | 0.015 | | |
| | Fe–Fe2 | 3.43(1) | 4.65(68) | 0.015 | | |

^a Inter-atomic distances. ^b Coordination numbers. ^c Debye–Waller factors of Fe–O and Fe–Fe. The Debye–Waller factors of all samples were around 0.011 for Fe–O and 0.015 for Fe–Fe determined from the R -space fit. Then, the Debye–Waller factors of Fe–O and Fe–Fe of all samples were fixed to these values to allow an equal comparison of the other parameters. ^d ΔE_0 is the threshold energy correction. ^e R -factor indicates the goodness of the fits.

the Fe–Fe2 distance of 3.43 ± 0.02 Å correspond to, respectively, two edge-sharing FeO₆ octahedra and two bent corner-sharing FeO₆ octahedra or to corner sharing between an FeO₆ octahedron and an FeO₄ tetrahedron.^{27,52} Further, these

values are in good agreement with the PDF results (Fig. 2c). With the crystallite size increasing from 2LFh_1 to 6LFh_4, the CNs of Fe–Fe1 and Fe–Fe2 increase from 2.50 ± 0.40 to 2.84 ± 0.50 and from 3.71 ± 0.55 to 4.65 ± 0.68 , respectively.



The general conclusion based on the analysis results of the XRD, PDF and X-ray absorption spectra is that the studied samples possess a common long-, medium- and local-range structure. The ferrihydrite crystallite size has little influence on the average Fe–O, Fe–Fe1 and Fe–Fe2 coordination distances, but the average Fe–Fe CNs increase with increasing size of the ferrihydrite crystallites. The variation of CNs is consistent with classic particle size effects, *i.e.*, smaller particles have less neighboring Fe atoms around each Fe center because the percentages of the surface Fe sites increase with decreasing size, leading to less neighboring Fe. In addition, this also implies a weaker order of Fe–Fe arrangements for smaller ferrihydrites, whereas the location of the disorder could not be revealed. In the next section, it will be shown that the analysis of the Mössbauer spectra at 295 K provides further information.

Mössbauer spectra at room temperature

At 295 K, the Mössbauer spectra of all ferrihydrite samples present a paramagnetic doublet (Fig. 4a and b). The first set of average parameters was obtained by fitting the spectra with one doublet (Fig. 4a). The results show (Table 3) that the central shifts (C_s) for samples of different sizes are close to each other and range from 0.343 to 0.360 mm s⁻¹; the quadrupole splittings (Q_s) range from 0.717 to 0.625 mm s⁻¹ and show a decreasing trend with increasing crystallite size. These values are consistent with the one-doublet fitting results previously reported.^{31,54} However, due to the broad doublets and high line widths observed in the present samples, the use of only one doublet is insufficient for good fits; this is also indicated by the high χ^2 values (Table 3).

Using two doublets provides better fits of the spectra (Table 3) and may allow for a distinction between the core and surface regions of the particles.^{55–57} The range of C_s values is similar to that for one-doublet fitting and the variation in the C_s values is not correlated with the crystallite size of the

ferrihydrites. The Q_s values of the ferrihydrite samples obtained with two-doublet fitting slightly decrease (for both sites) with increasing crystallite size. According to Cornell and Schwertmann,² relatively high Q_s values correspond to a high degree of distortion of FeO₆ octahedra. Therefore, the present results indicate that the degree of distortion of the FeO₆ octahedra increases with decreasing crystallite size, similar to the results of one-doublet fitting. Additionally, the Q_s values for doublet 1 are larger than those for doublet 2, implying that doublet 1 belongs to FeO₆ octahedra in the surface layer.²

The site populations of doublet 2 (core) are larger than those of doublet 1 (layer), and the difference between them increases with increasing crystallite size, which results from an increasing surface layer contribution with decreasing crystallite size. The site population of doublet 1 is plotted against the crystallite size, wherein a gradually decreasing trend is observed for the site population with crystallite size. The magnitude of the site population of doublet 1 is approximately 40% for 2LFh_1 and 5LFh_2 and approximately 33% for 5LFh_3 and 6LFh_4. These results indicate that the contribution of the surface layer increases with decreasing crystallite size. As the surface layer becomes more disordered (higher Q_s) than the core, the disorder will progressively increase with decreasing crystallite size. The combination of this information with the PDF fitting results (a certain amount of Fe vacancies exists in the structure) indicates that the disordered surface structure is derived from the random arrangement of Fe vacancies at or near the surface as well as minor stacking faults. The observation that the disorder of the surface layer increases with decreasing crystallite size is consistent with the variation of Fe vacancies as a function of size, as obtained from the PDF fitting (Table 1). In other words, crystallites with a smaller size have a higher amount of Fe2 and Fe3 vacancies, which leads to a higher degree of disorder in the surface layer. These results support Hiemstra's surface-depletion model,¹⁷ *i.e.*, the surface layer of ferrihydrite is depleted by Fe2 and Fe3 and smaller



Fig. 4 Mössbauer spectra of the ferrihydrite samples (symbols). Panels (a) and (b) show the results at 295 K and their fits with one Lorentzian doublet (blue curves) or with two Lorentzian doublets (blue curves); the red curves show the two contributions. Panel (c) depicts the spectra at 20 K and their fits with doublets and sextets (blue curves); the red curves show the doublet and sextet contributions.



Table 3 Room-temperature Mössbauer parameters of the four synthetic ferrihydrites fitted with one doublet and two doublets. The values in brackets are fitting errors

| Samples | Fitting modes | Fitting parameters | | | | |
|---------|----------------|--------------------|-----------------------------|-----------------------------|---------------------|----------|
| | | Reduced χ^2 | C_s (mm s ⁻¹) | Q_s (mm s ⁻¹) | Site population (%) | |
| 2LFh_1 | Single doublet | 15.97 | 0.347(1) | 0.717(1) | 100 | |
| | Two doublets | Site 1 | 2.67 | 0.343(9) | 0.994(14) | 38.4(32) |
| | | Site 2 | | 0.347(6) | 0.566(9) | 61.6(32) |
| 5LFh_2 | Single doublet | 12.97 | 0.355(1) | 0.684(1) | 100 | |
| | Two doublets | Site 1 | 1.95 | 0.342(10) | 0.937(16) | 41.9(37) |
| | | Site 2 | | 0.357(6) | 0.541(9) | 58.1(36) |
| 5LFh_3 | Single doublet | 3.71 | 0.343(1) | 0.625(1) | 100 | |
| | Two doublets | Site 1 | 1.11 | 0.334(18) | 0.894(29) | 31.7(73) |
| | | Site 2 | | 0.346(11) | 0.509(18) | 68.3(73) |
| 6LFh_4 | Single doublet | 10.18 | 0.360(1) | 0.664(1) | 100 | |
| | Two doublets | Site 1 | 3.66 | 0.350(2) | 0.938(7) | 33.9(78) |
| | | Site 2 | | 0.367(1) | 0.556(2) | 66.1(78) |

ferrihydrites have a higher percentage of poorly coordinated Fe sites in the surface layer.

Magnetic hyperfine splitting at low temperature

At 20 K, the Mössbauer spectra of the ferrihydrite samples show magnetic hyperfine splitting due to the weakness or even disappearance of the relaxation effect caused by their superparamagnetic behavior.^{51,58,59} The degree of splitting is related to the crystallite size (Fig. 4c and Table SI-2†). The spectra of samples 2LFh_1 and 5LFh_2, which have a relatively small size, split doublet 2 at 295 K into one sextet at 20 K, while samples 5LFh_3 and 6LFh_4, which have a relatively large size, split the two doublets at 295 K into two sextets at 20 K (Fig. 4). Therefore, the ferrihydrite samples have no definite magnetic-ordering temperature, but they order magnetically at varying temperatures, as determined by their crystallite size. This is consistent with the report of Schwertmann *et al.*,³⁵ who suggested that a ferrihydrite with a smaller crystallite size (formed at a higher Fe³⁺ hydrolysis rate) had a

lower magnetic ordering temperature. In addition, the Mössbauer spectra at room temperature of different-sized BiFeO₃ nanoparticles also show a similar trend with size.⁵⁸ Comparing the Mössbauer spectra of the ferrihydrite samples at 20 K, the intensities of the sextet peaks increase and the spectral line widths significantly decrease with increasing crystallite size; this can be ascribed to the decrease of the superparamagnetic behavior with increasing size. The hyperfine splitting and hyperfine magnetic-field intensity decrease with decreasing crystallite size (Table SI-2†). Below a certain crystallite size, the hyperfine splitting is suppressed. The suppression of the material's intrinsic spin may be caused by uncompensated spins at the surface, strain anisotropies and noncollinear magnetic ordering.⁵⁸ In the present situation, the quadrupole splitting results indicate that, especially for particles with relatively small crystallite sizes, a large part of the disorder is located in the surface layer; therefore, uncompensated spins in the surface layer will be the main reason for the reduced hyperfine splitting and reduced magnetic-field intensity.

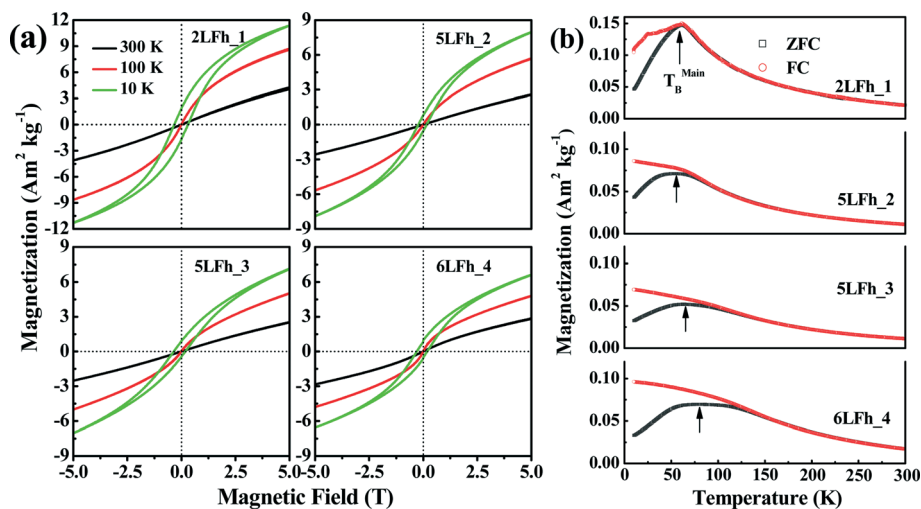


Fig. 5 Magnetization of the four ferrihydrite samples. Panel (a) shows the hysteresis loops measured at 10, 100 and 300 K. Note that the hysteresis loops did not attain saturation at 5 T. Panel (b) shows the zero field-cooled (ZFC, black) and field-cooled (FC, red) induced magnetizations obtained with an applied field of 20 mT.



Table 4 Primary magnetic parameters at different temperatures for ferrihydrites of different sizes

| Temperatures | 10 K | | | 100 K | 300 K | |
|--------------|----------------|---|---|---|---|----------------------------|
| Parameters | Coercivity (T) | Remanent magnetization ($\text{A m}^2 \text{ kg}^{-1}$) | Magnetization at 5 T ($\text{A m}^2 \text{ kg}^{-1}$) | Magnetization at 5 T ($\text{A m}^2 \text{ kg}^{-1}$) | Magnetization at 5 T ($\text{A m}^2 \text{ kg}^{-1}$) | Unblocking temperature (K) |
| 2LFh_1 | 0.30 | 1.84 | 11.37 | 8.60 | 4.26 | 60 |
| 5LFh_2 | 0.16 | 0.79 | 7.97 | 5.66 | 2.59 | 60 |
| 5LFh_3 | 0.18 | 0.89 | 7.15 | 5.01 | 2.54 | 65 |
| 6LFh_4 | 0.18 | 0.93 | 6.63 | 4.79 | 2.86 | 80 |

Magnetization hysteresis loops and ZFC-FC curves

The magnetization curves measured at 10, 100 and 300 K are shown in Fig. 5a. The shape of the magnetization curves depends on both the measurement temperature and crystallite size. Overall, the magnetization curves are nearly linear at 300 K and have a sigmoidal shape at 100 K and 10 K. A clear hysteresis loop is observed only at 10 K and none of the samples are saturated in magnetization at 5 T. The non-saturated linear pattern indicates a paramagnetic component, which is consistent with the Mössbauer results at room temperature, while the sigmoidal pattern suggests the presence of a saturated superparamagnetic component.⁶⁰

At 10 K, the remanent magnetizations for the studied samples range from 0.79 to 1.84 $\text{A m}^2 \text{ kg}^{-1}$, and the coercivities (B_c) are in the range of 0.16 to 0.30 T (Table 4). This indicates that ferrihydrite is paramagnetic at room temperature but is magnetically ordered at very low temperatures, *e.g.*, ferromagnetic-like moment. A similar magnetic behavior has been reported by Guyodo *et al.*³² for 6LFh samples of different sizes, by Michel *et al.*¹⁸ for ferrifh and by Berquó *et al.*³⁴ for Si-incorporated ferrihydrites of sizes ranging from 1 to 25 nm.

The dependence of magnetization at an applied field of 5 T on crystallite size is shown in Fig. 6a. With increasing crystallite size, the magnetization of the ferrihydrite samples

decreases. With increasing temperature, the magnetization also decreases (Fig. 6a and Table 4).

The ZFC (black) and FC (red) curves are shown in Fig. 5b. For antiferromagnetic minerals with high coercivity, the ZFC curve is analogous to the curve of temperature-dependent magnetic susceptibility, and the peak in the ZFC curve signifies the unblocking temperature (T_B) (Fig. 5b).³⁴ The broadening of peaks in the ZFC curves with increasing crystallite size likely reflects the widening of the crystallite size distribution with increasing average crystallite size. It also emphasizes that the peak presents the average T_B indicated by the arrows in Fig. 5b. The FC curve is enhanced at low temperature compared to the ZFC curve because an additional thermal remanent magnetization is acquired. The point where the FC and ZFC curves converge is also an indication of T_B . The T_B obtained from the convergence point corresponds to the maximum estimate of T_B . With increasing crystallite size, the average T_B and maximum estimate of T_B slightly increase from approximately 60 to 80–100 K, and the largest increase is observed between 5LFh_3 and 6LFh_4 (Table 4).

In summary, the present magnetization results confirm that ferrihydrite is antiferromagnetic with a small ferromagnetic-like moment at low temperatures. In general, a ferromagnetic-like moment can originate from either the uncompensated spins present inside the particles and/or at the surface of the particles^{32,60} or, for large particles, the



Fig. 6 Magnetization characteristics as a function of crystallite size. Panel (a) shows the magnetization of the four ferrihydrites for an applied field of 5 T and at three temperatures. Panel (b) shows the unblocking temperature (T_B) of various ferrihydrites and maghemite as a function of grain size. The data from the present study (blue squares) are compared with theoretical maghemite data taken from Liu *et al.*,³ 6LFh data from Guyodo *et al.*,³² and data for Si-incorporated ferrihydrites from Berquó *et al.*³⁴



arrangement of magnetic moments at tetrahedral and octahedral Fe sites.¹⁸ For our extremely fine-grained particles, the latter mechanism is not applicable; therefore, uncompensated spins present inside the particles and/or in the surface layer should be responsible for the ferromagnetic-like moment. The Mössbauer data at room temperature have shown that the disorder is largely located in the surface layer. Therefore, the uncompensated spins in the surface layer will lead to the small ferromagnetic-like moments.

Discussion

Presence of tetrahedral coordination of Fe in ferrihydrite

It has been reported that the shape, position and intensity of the pre-edge peak of the Fe K-edge XAS are related to the oxidation state and coordination of Fe in minerals.⁶¹ However, the interpretation of this peak for ferrihydrite is debated. Zhao *et al.*⁵¹ found that the pre-edge peak area of ferrihydrite was significantly larger (20–80%) than those of goethite and hematite, which have only the octahedral coordination of Fe, and slightly smaller than that of magnetite (~36%) with tetrahedral coordination. Therefore, they inferred that ferrihydrite samples may contain 20–30% tetrahedral coordination. In contrast, some years later, Manceau and Gates⁴⁹ found that the peak area of ferrihydrite is only 0–20% larger than that of hematite and suggested that the increase in peak area is related not only to the CNs of Fe but also to the geometry of the Fe sites; they claimed that almost all Fe existed in octahedral coordination and that the pre-edge peak cannot be used to determine the percentage of tetrahedral coordination.

When the peak areas of the present ferrihydrite samples are compared with those of goethite, hematite and magnetite (Fig. 7), the results are similar to those of Zhao *et al.* The peak areas of the ferrihydrite samples are considerably greater than those of goethite and hematite, but somewhat smaller than that of magnetite. According to the PDF analysis, the relative Fe³⁺ (tetrahedral Fe) site occupancy of the present samples ranges from 0.82 to 0.88 (Table 1).



Fig. 7 Comparison of the Fe K-edge XAS pre-edge peaks among magnetite, hematite, goethite and the four ferrihydrite samples.

Additionally, the results of PDF and XAS fitting show that the second Fe–Fe coordination distance is approximately 3.44 Å (Fig. 2 and Table 2), which is consistent with the reports of Michel *et al.*⁴⁷ and Xu *et al.*²⁷ According to Xu *et al.*,²⁷ an Fe–Fe coordination distance of 3.44 Å can serve as indirect evidence of the presence of tetrahedral Fe. Consideration of the additional information about tetrahedral Fe in combination with the present agreement with Zhao's results suggests that Zhao's conclusion is sound. However, we have no further arguments to oppose the view of Manceau and Gates.

Effects of crystallite size on the structure of ferrihydrite

In spite of great advancements towards revealing the basic structure of ferrihydrite in previous studies,^{18,21,23} there remain disputes over the bulk and surface structures of ferrihydrite with a wide range of grain sizes. This has hindered an accurate understanding of the grain size-dependent properties of ferrihydrite. Our results indicate that ferrihydrites with different crystallite sizes share a common short-, medium- and long-range structure (Fig. 1–3). Given that the “ordered” ferrihydrite with a large size (*i.e.*, ferrifh, 10–12 nm, Michel *et al.*¹⁸) shares a PDF similar to 2LFh, it is suggested that ferrihydrites with different sizes possess a relatively stable bulk or core structure. This is confirmed by the present XRD, PDF and XAS data of the ferrihydrite samples with different crystallite sizes (1.6–4.4 nm), similar to those of the commonly found fine-grained natural ferrihydrites.

Nevertheless, the results also indicate a certain degree of distortion: the average Fe–Fe CNs increase with increasing size of the ferrihydrite crystallites (Table 2). A similar increase has been observed in Al–Fe oxyhydroxide co-precipitates^{42,52} and hydroxybenzoic acid–Fe co-precipitates.⁵⁰ In addition, anisotropic variations in lattice dimensions indicate size-dependent structural relaxation in ferrihydrite (Table 1), consistent with a reduction in strain with increasing crystallite size.¹⁸ A certain number of Fe vacancies exist in the ferrihydrite structure, and Fe vacancies/defects increase with decreasing ferrihydrite crystallite size (Table 1). The combination of these results with a detailed analysis of the Mössbauer spectra at 295 K leads to the conclusion that the surface layer is the region with higher disorder (Table 3) and that the smaller ferrihydrites have a higher percentage of poorly coordinated Fe sites in the surface layer. In summary, the present results support the view that the particle cores have the same structure, that the surface layer is relatively disordered, and that the latter disorder increases with decreasing crystallite size; they therefore support the ferrihydrite structure model suggested by Hiemstra.¹⁷

Based on electron diffraction analysis, Janney *et al.*^{62,63} concluded that 6LFh was distinctly different from 2LFh. They found that 2LFh contained highly disordered material and crystallites with structures based on the hexagonal and cubic stacking of close-packed layers of O²⁻ and OH⁻ ions, while 6LFh contained structures based on the double-hexagonal stacking of close-packed layers of O²⁻. Clearly, these results



indicate greater differences between 2LFh and 6LFh than those indicated by the present results. Although the basic core structure remains the same with varying crystallite size, the PDF and XAS fitting results indicate that the unit cell parameters, Fe occupancies and Fe–Fe coordination numbers all change somewhat with crystallite size (Tables 1 and 2). Therefore, the structure of the 2LFh particles is different from that of the 6LFh particles. The present results are in good agreement with several other reports, which suggested that the primary difference among ferrihydrites of different sizes is the size of the coherent scattering domain.^{16,32,47}

Magnetization of ferrihydrite and its environmental application

With accurate constraints on the structure of the studied ferrihydrite samples, the origin and grain size dependence of their magnetism can be well resolved. The present results confirm that ferrihydrite shows antiferromagnetism superimposed with a small ferromagnetic-like moment at low temperatures and that the ferromagnetic-like moment is largely due to the uncompensated spins in the surface layer. For nano-sized strongly magnetic particles, such as magnetite⁶⁴ or ferrifh (ordered ferrihydrite),¹⁸ the presence of uncompensated surface spins weakens the bulk magnetic properties, resulting in a positive correlation between grain size and magnetization. In contrast, the magnetization of nano-sized antiferromagnetic minerals such as hematite originates from uncompensated surface spins, and a negative correlation between magnetization and grain size was observed.⁶⁵ Similar to hematite, the magnetization at 5 T of the studied ferrihydrites gradually increases with decreasing size (Table 4 and Fig. 6a). It should be noted that the smallest sample, 2LFh_1, has much higher values of B_c and magnetization than the other samples. We tentatively interpret that the elevated coercivity B_c is due to either the enhanced surface anisotropy or the enhanced stress between the core and surface shell. Such a stress has also been used to explain the higher B_c values of the low-temperature oxidized magnetite with a stoichiometric magnetite core surrounded by a maghemite shell.⁶⁶ The much higher magnetization of 2LFh_1 further indicates that the uncompensated spins in the surface layer could also significantly contribute to its bulk magnetization because of its poor crystallinity.

For the studied ferrihydrites, the surface layer structure most likely dominates the changes in magnetism with size, and the decrease in magnetization with increasing size could be attributed to the lowering of uncompensated surface spins. This is in contrast with the behavior of ordered and larger ferrihydrites (ferrifh),¹⁸ in which the bulk structure dominates and the ordering of electron spin moments of the bulk Fe accounts for the enhancement in magnetism with increasing size. Considering the opposite magnetization trends observed for the present particles (1.6–4.4 nm, Fig. 6a) and ferrifh (10–12 nm), we predict that with a continuously increasing size of ferrihydrites from small disordered particles

to relatively large ordered crystallites, there is likely a transient point at which the magnetization is minimum. If this is true, a gradual transformation of relatively smaller 2LFh with crystallite sizes of several nm into relatively larger ferrihydrites with crystallite sizes of 10–12 nm might first result in a decrease in magnetism followed by a significant increase in magnetism.

As ferrihydrite is the most important precursor for other secondary magnetic minerals formed through pedogenesis (e.g., ferrifh, magnetite and maghemite),^{3,18} the magnetic properties of ferrihydrite with different sizes are important for determining the evolution of the related minerals and explaining the magnetic enhancement in aerobic soils. Therefore, to understand the environmental significance of ferrihydrite in natural samples, it is essential to have information on the ferrihydrite grain size. In Fig. 6b, we summarize the correlation between the T_B and grain size of synthetic ferrihydrites. Compared to the theoretical curve for maghemite,³ ferrihydrites have much higher unblocking temperatures due to their higher anisotropy constants. For the extremely fine-grained ferrihydrites (1–5 nm), variation in the values of T_B exists among samples with similar sizes synthesized under different conditions (Fig. 6b). For ferrihydrite samples in the grain-size range (~1–10 nm), the decrease in crystallite size and the presence of Si both lead to the decrease in T_B (Fig. 6b). This strongly indicates that the distribution of the uncompensated surface spins of ferrihydrites as well as their grain sizes affect T_B . Such complexity should be considered when constructing the relationship between ferrihydrites and other iron oxides in natural samples. Nevertheless, an overall positive correlation exists between T_B and the grain size of ferrihydrites; thus, T_B is anyhow a useful and practical proxy to quantify the changes in the grain size of ferrihydrites in natural samples provided that the natural conditions are relatively similar.

Conclusions

The structural characterization of the present samples based on the Michel model parameters reveals that ferrihydrite samples with small grains share a common short-, medium- and long-range structure with a large size of ferrihydrite (*i.e.*, ferrifh). Meanwhile, both the average CNs of Fe–Fe and Fe2 and Fe3 occupancies increase with crystallite size, suggesting that smaller ferrihydrites exhibit higher structural disorder. Further, the Mössbauer results at 295 K indicate that the surface layer is relatively disordered, which might be caused by the randomly distributed Fe vacancies at or near the surface and minor stacking faults. This observation supports Hiemstra's surface-depletion model in terms of the location of disorder and the variations of Fe2 and Fe3 occupancies with size. This clarification of the relationship between the ferrihydrite size and structure, and especially the surface structure, is useful for understanding and exploring the adsorption on ferrihydrites and its interaction with other nanoparticles in natural environments.



Magnetic data verify that ferrihydrite samples show anti-ferromagnetism with a ferromagnetic-like moment at lower temperatures (100 K and 10 K), but they are paramagnetic at room temperature (300 K). Smaller ferrihydrites show less magnetic hyperfine splitting and a lower unblocking temperature (T_B). In addition, magnetization decreases with increasing crystallite size for disordered ferrihydrite, while an enhancement in magnetism with increasing size is shown for ordered ferrihydrite. It is therefore predicted that with increasing size of ferrihydrites, a transient point occurs at which the magnetization is minimum. Considering that the transformation of ferrihydrite to different iron oxides plays an important role in the mineralogical evolution of iron oxides and magnetic enhancement during pedogenesis, the size-dependent structure and magnetic properties of disordered ferrihydrite provide important basic information for better understanding of these evolution processes.

Acknowledgements

The authors gratefully acknowledge the National Natural Science Foundation of China (NSFC Grant No. 41471194 and 41571448) and the Strategic Priority Research Program of the Chinese Academy of Sciences (No. XDB15020402) for financial support to this research. The U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences supported the use of the National Synchrotron Light Source, Brookhaven National Laboratory under contract no. DE-AC02-98CH10886. We greatly thank Prof. Dejun Fu and Dr. Renzheng Xiao at Wuhan University for their support with Mössbauer spectra collection and analyses. We are grateful to the associate editor and two anonymous reviewers who helped improve the manuscript considerably.

References

- J. L. Jambor and J. E. Dutrizac, *Chem. Rev.*, 1998, **98**, 2549–2585.
- R. M. Cornell and U. Schwertmann, *The Iron Oxides: Structure, Properties, Reactions, Occurrences and Uses*, Wiley-VCH, Weinheim, Germany, 2003.
- Q. S. Liu, V. Barron, J. Torrent, S. G. Eeckhout and C. L. Deng, *J. Geophys. Res.: Solid Earth*, 2008, **113**, B01103.
- Q. S. Liu, A. P. Roberts, J. C. Larrasoana, S. K. Banerjee, Y. Guyodo, L. Tauxe and F. Oldfield, *Rev. Geophys.*, 2012, **50**, RG4002.
- X. M. Wang, M. Q. Zhu, S. Lan, M. Ginder-Vogel, F. Liu and X. H. Feng, *Chem. Geol.*, 2015, **415**, 37–46.
- M. F. Hochella, S. K. Lower, P. A. Maurice, R. L. Penn, N. Sahai, D. L. Sparks and B. S. Twining, *Science*, 2008, **319**, 1631–1635.
- A. C. Cismasu, C. Levard, F. M. Michel and G. E. Brown, *Geochim. Cosmochim. Acta*, 2013, **119**, 46–60.
- N. Pinney and D. Morgan, *Geochim. Cosmochim. Acta*, 2013, **120**, 514–530.
- M. F. Hochella, T. Kasama, A. Putnis, C. V. Putnis and J. N. Moore, *Am. Mineral.*, 2005, **90**, 718–724.
- K. Kaiser, R. Mikutta and G. Guggenberger, *Soil Sci. Soc. Am. J.*, 2007, **71**, 711–719.
- F. E. Rhoton, M. J. M. Romkens, J. M. Bigham, T. M. Zobeck and D. R. Upchurch, *Soil Sci. Soc. Am. J.*, 2003, **67**, 1220–1226.
- J. Filip, R. Zboril, O. Schneeweiss, J. Zeman, M. Cernik, P. Kvapil and M. Otyepka, *Environ. Sci. Technol.*, 2007, **41**, 4367–4374.
- X. M. Wang, W. Li, R. Harrington, F. Liu, J. B. Parise, X. H. Feng and D. L. Sparks, *Environ. Sci. Technol.*, 2013, **47**, 10322–10331.
- A. Voegelin and S. J. Hug, *Environ. Sci. Technol.*, 2003, **37**, 972–978.
- A. C. Scheinost, S. Abend, K. I. Pandya and D. L. Sparks, *Environ. Sci. Technol.*, 2001, **35**, 1090–1096.
- V. A. Drits, B. A. Sakharov, A. L. Salyn and A. Manceau, *Clay Miner.*, 1993, **28**, 185–207.
- T. Hiemstra, *Geochim. Cosmochim. Acta*, 2013, **105**, 316–325.
- F. M. Michel, V. Barron, J. Torrent, M. P. Morales, C. J. Serna, J. F. Boily, Q. S. Liu, A. Ambrosini, A. C. Cismasu and G. E. Brown, *Proc. Natl. Acad. Sci. U. S. A.*, 2010, **107**, 2787–2792.
- A. Navrotsky, L. Mazeina and J. Majzlan, *Geochim. Cosmochim. Acta*, 2008, **72**, A673–A673.
- T. Hiemstra, *Geochim. Cosmochim. Acta*, 2015, **158**, 179–198.
- F. M. Michel, L. Ehm, S. M. Antao, P. L. Lee, P. J. Chupas, G. Liu, D. R. Strongin, M. A. A. Schoonen, B. L. Phillips and J. B. Parise, *Science*, 2007, **316**, 1726–1729.
- W. H. Casey, *Chem. Rev.*, 2006, **106**, 1–16.
- O. Sadeghi, L. N. Zakharov and M. Nyman, *Science*, 2015, **347**, 1359–1362.
- A. Manceau, *Am. Mineral.*, 2011, **96**, 521–533.
- A. Manceau, *Clay Miner.*, 2009, **44**, 19–34.
- D. G. Rancourt and J. F. Meunier, *Am. Mineral.*, 2008, **93**, 1412–1417.
- W. Q. Xu, D. B. Hausner, R. Harrington, P. L. Lee, D. R. Strongin and J. B. Parise, *Am. Mineral.*, 2011, **96**, 513–520.
- Z. X. Jiang, Q. S. Liu, C. Colombo, V. Barron, J. Torrent and P. X. Hu, *Geophys. J. Int.*, 2014, **196**, 131–144.
- G. Rubasinghege, R. W. Lentz, M. M. Scherer and V. H. Grassian, *Proc. Natl. Acad. Sci. U. S. A.*, 2010, **107**, 6628–6633.
- S. Laurent, D. Forge, M. Port, A. Roch, C. Robic, L. V. Elst and R. N. Muller, *Chem. Rev.*, 2008, **108**, 2064–2110.
- H. Tuysuz, E. L. Salabas, C. Weidenthaler and F. Schuth, *J. Am. Chem. Soc.*, 2008, **130**, 280–287.
- Y. Guyodo, S. K. Banerjee, R. L. Penn, D. Burleson, T. S. Berquó, T. Seda and P. Solheid, *Phys. Earth Planet. Inter.*, 2006, **154**, 222–233.
- V. Barron, J. Torrent and E. de Grave, *Am. Mineral.*, 2003, **88**, 1679–1688.
- T. S. Berquó, S. K. Banerjee, R. G. Ford, R. L. Penn and T. Pichler, *J. Geophys. Res.: Solid Earth*, 2007, **112**, B02102.
- U. Schwertmann, J. I. Friedl and A. Kyek, *Clays Clay Miner.*, 2004, **52**, 221–226.
- J. J. Erbs, B. Gilbert and R. L. Penn, *J. Phys. Chem. C*, 2008, **112**, 12127–12133.



- 37 P. J. Chupas, X. Y. Qiu, J. C. Hanson, P. L. Lee, C. P. Grey and S. J. L. Billinge, *J. Appl. Crystallogr.*, 2003, **36**, 1342–1347.
- 38 A. P. Hammersley, *ESRF Internal Report, ESRF98HA01T, FIT2D V9.129 Reference Manual V3.1.*, 1998.
- 39 X. Qiu, J. W. Thompson and S. J. L. Billinge, *J. Appl. Crystallogr.*, 2004, **37**, 678.
- 40 C. L. Farrow, P. Juhás, J. W. Liu, D. Bryndin, E. S. Bozin, J. Bloch, T. Proffen and S. J. L. Billinge, *J. Phys.: Condens. Matter*, 2007, **19**, 335219.
- 41 B. Ravel and M. Newville, *J. Synchrotron Radiat.*, 2005, **12**, 537–541.
- 42 A. Hofmann, D. Vantelon, E. Montarges-Pelletier, F. Villain, O. Gardoll, A. Razafitianamaharavo and J. Ghanbaja, *J. Colloid Interface Sci.*, 2013, **407**, 76–88.
- 43 A. L. Ankudinov and J. J. Rehr, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1997, **56**, R1712–R1715.
- 44 E. Murad and J. Cashion, *Mössbauer Spectroscopy of Environmental Materials and Their Industrial Utilization*, Klüwer Academic Publication, Dordrecht, the Netherlands, 2004.
- 45 A. Neumann, T. L. Olson and M. M. Scherer, *Environ. Sci. Technol.*, 2013, **47**, 6969–6977.
- 46 K. Lagarec and D. G. Rancourt, *Recoil-Mössbauer Spectral Analysis Software for Windows*, Department of Physics, University of Ottawa, Ontario, 1998.
- 47 F. M. Michel, L. Ehm, G. Liu, W. Q. Han, S. M. Antao, P. J. Chupas, P. L. Lee, K. Knorr, H. Eulert, J. Kim, C. P. Grey, A. J. Celestian, J. Gillow, M. A. A. Schoonen, D. R. Strongin and J. B. Parise, *Chem. Mater.*, 2007, **19**, 1489–1496.
- 48 M. Q. Zhu, C. L. Farrow, J. E. Post, K. J. T. Livi, S. J. L. Billinge, M. Ginder-Vogel and D. L. Sparks, *Geochim. Cosmochim. Acta*, 2012, **81**, 39–55.
- 49 A. Manceau and W. P. Gates, *Clays Clay Miner.*, 1997, **45**, 448–460.
- 50 C. Mikutta, *Geochim. Cosmochim. Acta*, 2011, **75**, 5122–5139.
- 51 J. M. Zhao, F. E. Huggins, Z. Feng and G. P. Huffman, *Clays Clay Miner.*, 1994, **42**, 737–746.
- 52 Y. T. Liu and D. Hesterberg, *Environ. Sci. Technol.*, 2011, **45**, 6283–6289.
- 53 F. Maillot, G. Morin, Y. H. Wang, D. Bonnin, P. Ildefonse, C. Chaneac and G. Calas, *Geochim. Cosmochim. Acta*, 2011, **75**, 2708–2720.
- 54 J. G. Stevens, A. M. Khasanov and D. R. Mabe, *Hyperfine Interact.*, 2005, **161**, 83–92.
- 55 E. Murad, *Phys. Chem. Miner.*, 1996, **23**, 248–262.
- 56 E. Murad and U. Schwertmann, *Am. Mineral.*, 1980, **65**, 1044–1049.
- 57 A. M. van der Kraan, *Phys. Status Solidi A*, 1973, **18**, 215–226.
- 58 T. J. Park, G. C. Papaefthymiou, A. J. Viescas, A. R. Moodenbaugh and S. S. Wong, *Nano Lett.*, 2007, **7**, 766–772.
- 59 A. Hartnett, L. H. Bottger, B. F. Matzanke and C. J. Carrano, *J. Inorg. Biochem.*, 2012, **116**, 188–194.
- 60 R. S. Zergenyi, A. M. Hirt, S. Zimmermann, J. P. Dobson and W. Lowrie, *J. Geophys. Res.: Solid Earth*, 2000, **105**, 8297–8303.
- 61 M. Wilke, F. Farges, P. E. Petit, G. E. Brown and F. Martin, *Am. Mineral.*, 2001, **86**, 714–730.
- 62 D. E. Janney, J. M. Cowley and P. R. Buseck, *Am. Mineral.*, 2000, **85**, 1180–1187.
- 63 D. E. Janney, J. M. Cowley and P. R. Buseck, *Am. Mineral.*, 2001, **86**, 327–335.
- 64 M. P. Morales, S. Veintemillas-Verdaguer, M. I. Montero, C. J. Serna, A. Roig, L. Casas, B. Martinez and F. Sandiumenge, *Chem. Mater.*, 1999, **11**, 3058–3064.
- 65 Z. X. Jiang, Q. S. Liu, V. Barron, J. Torrent and Y. J. Yu, *J. Geophys. Res.: Solid Earth*, 2012, **117**, B02102.
- 66 Q. S. Liu, S. K. Banerjee, M. J. Jackson, C. L. Deng, Y. X. Pan and R. X. Zhu, *Geophys. J. Int.*, 2004, **158**, 506–514.

