

Cite this: *Chem. Sci.*, 2016, 7, 451

2-(Anthracenyl)-4,5-bis(2,5-dimethyl(3-thienyl))-1H-imidazole: regulatable stacking structures, reversible grinding- and heating-induced emission switching, and solid-state photodimerization behavior†

Jun-Feng Chen,^a Dan-Ping Gong,^a Jing Wen,^b Haibo Ma^b and Deng-Ke Cao^{*a}

2-(Anthracenyl)-4,5-bis(2,5-dimethyl(3-thienyl))-1H-imidazole (anbdtiH) has been synthesized. Its three solid-state structures, anbdtiH·CH₃Cl (**1**), anbdtiH·2CH₃OH (**2**) and anbdtiH₂·CF₃COO·CH₃OH·H₂O (**3**), have been constructed by skillfully choosing CHCl₃ or CH₃OH as the solvent and using or not using CF₃COOH, with the aim of modifying the intermolecular hydrogen bonds and/or $\pi\cdots\pi$ stacking interactions. The three distinct structures show significantly different solid-state luminescence behaviors, an orange-red emission at 603 nm for **1**, a blue emission at 453 nm for **2**, and a green emission at 533 nm for **3**. Upon grinding, these emission wavelengths exhibit evident variations, a blue-shift of $\Delta\lambda = 83$ nm for **1**, a red-shift of $\Delta\lambda = 20$ nm for **2**, and a blue-shift of $\Delta\lambda = 54$ nm for **3**. The emission color of **1** can be reversibly switched between orange-red and green upon regulation of the intermolecular (N–H)_{imidazole}⋯N_{imidazole} hydrogen bonds by a grinding–heating process. Moreover, compound **3** can undergo a solid-state [4 π + 4 π] photodimerization reaction upon irradiation with sunlight, forming **3-dimer**. Based on the crystal structures of **1–3**, this work discusses the relationship between the molecular stacking mode and the luminescence behavior/photochemical reactivity.

Received 27th August 2015
Accepted 7th October 2015

DOI: 10.1039/c5sc03201f

www.rsc.org/chemicalscience

Introduction

In solid-state organic molecular materials, the molecular stacking mode plays a key role in obtaining the desired physical and chemical properties.¹ Intermolecular hydrogen bonds and $\pi\cdots\pi$ stacking are two kinds of main supramolecular interactions, which could regulate the molecular stacking mode, thus leading to different functional properties, such as stimuli-responsive luminescence,² and photochemical reactivity.³ Considerable attention has been focused on anthracene derivatives, mainly because of their intriguing luminescent properties^{4–8} and interesting [4 π + 4 π] photodimerization behaviors.⁹ Several anthracene derivatives were found to show reversible emission changes induced by grinding and heating.^{6–8} For

example, Wang, Zhang *et al.* have reported 3(5)-(9-anthryl)pyrazole and its one derivative,⁶ which show different emission-color changes upon grinding, from blue to green and from green to blue, respectively. Tian *et al.* synthesized 9,10-bis((*E*)-2-(pyridin-2-yl)viny]anthracene (BP2VA) and 9,10-bis((*E*)-2-(pyridin-4-yl)viny]anthracene (BP4VA), each of which revealed a variety of emission colors from green to yellow upon grinding.⁷ Xiao, Yi *et al.* recently described four crystal structures of 2-(anthracen-9-yl)-4,5-diphenyl-1H-imidazole (ADPI) and their grinding-induced emission changes.⁸ Interestingly, the ground samples of these compounds could restore their initial emission colors upon heating at a temperature in the range of 90–170 °C.^{6–8} These stimuli-responsive luminescent materials have potential applications in rewritable optical media, information storage, imaging, sensors, switches,¹⁰ *etc.* Crystal-structure analyses indicate that the emission-color changes of these anthracene derivatives are mainly due to the regulation of the intermolecular $\pi\cdots\pi$ stacking interactions between the anthracene moieties by grinding and heating.^{6–8} This finding provides a guiding principle for the design and fabrication of anthracene-based molecular materials with grinding-/heating-responsive emissions. However, to this day, it is unclear whether we could use a grinding–heating process to regulate the intermolecular hydrogen bonds in an anthracene-based molecular material, thus resulting in grinding-/heating-

^aState Key Laboratory of Coordination Chemistry, School of Chemistry and Chemical Engineering, Nanjing University, Nanjing 210093, P. R. China. E-mail: dkcao@nju.edu.cn

^bKey Laboratory of Mesoscopic Chemistry of MOE, School of Chemistry and Chemical Engineering, Nanjing University, Nanjing 210093, P. R. China

† Electronic supplementary information (ESI) available: Physical measurements, syntheses, quantum chemical calculations, selected bond lengths, ¹H NMR spectra, XRD patterns, ATR IR spectra, diffuse reflectance spectra, luminescence spectra, photograph of the emission color, and crystal structures. CCDC 1415320–1415323. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c5sc03201f



Table 1 Crystallographic and refinement data for 1–3 and 3-dimer·2DMF

	1	2	3	3-dimer·2DMF
Formula	C ₃₀ H ₂₅ C ₁₃ N ₂ S ₂	C ₃₁ H ₃₂ O ₂ N ₂ S ₂	C ₃₂ H ₃₁ O ₄ N ₂ F ₃ S ₂	C ₆₄ H ₆₂ O ₂ N ₆ S ₄
<i>M</i>	583.99	528.71	628.71	1075.44
Crystal system	Hexagonal	Monoclinic	Monoclinic	Orthorhombic
Space group	<i>P</i> 6 ₅	<i>P</i> 2 ₁ / <i>c</i>	<i>P</i> 2 ₁ / <i>c</i>	<i>Pbca</i>
<i>a</i> /Å	13.8888(10)	22.178(6)	20.1561(15)	18.220(5)
<i>b</i> /Å	13.8888(10)	7.454(2)	9.0577(7)	12.964(4)
<i>c</i> /Å	25.754(4)	18.052(5)	17.1173(13)	24.265(7)
α /°	90	90	90	90
β /°	90	104.184(5)	93.2870(10)	90
γ /°	120	90	90	90
<i>V</i> /Å ³	4302.3(8)	2893.5(14)	3119.9(4)	5731(3)
<i>Z</i>	6	4	4	4
<i>D_c</i> /g cm ⁻³	1.352	1.214	1.338	1.246
<i>F</i> (000)	1812	1120	1312	2272
Goof on <i>F</i> ²	1.032	1.036	1.021	1.032
<i>R</i> ₁ , <i>wR</i> ₂ [<i>I</i> > 2σ(<i>I</i>)] ^a	0.0631, 0.1294	0.0554, 0.1224	0.0467, 0.1601	0.0698, 0.1470
<i>R</i> ₁ , <i>wR</i> ₂ (all data) ^a	0.1269, 0.1637	0.1234, 0.1468	0.0587, 0.1742	0.1672, 0.1789
(Δρ) _{max} , (Δρ) _{min} (e Å ⁻³)	0.275, -0.284	0.267, -0.274	0.429, -0.276	0.302, -0.270

$$^a R_1 = \frac{\sum ||F_o| - |F_c||}{\sum |F_o|}, wR_2 = \frac{[\sum w(F_o^2 - F_c^2)^2 / \sum w(F_o^2)^2]^{1/2}}{\sum w(F_o^2)^2}.$$



Fig. 1 Supramolecular left-handed chiral chain structure in 1.

Fig. 3 Supramolecular layer in 3. The large and medium red balls are the O atoms from the CH₃OH and H₂O molecules, respectively.Fig. 2 Supramolecular chain structure in 2. The red balls are the O atoms from the CH₃OH molecules.Fig. 4 The $\pi \cdots \pi$ stacking interactions between the anthracene moieties in 3. The red balls are the O atoms from the H₂O molecules.

nitrogen atom N1/N2 (Fig. 2) could result in a blue-shifted emission, which is confirmed by the emission spectra of anbdthH in different solvents (Fig. S10†). The emission in CH₃OH (498 nm) occurs at a shorter wavelength than the emission in toluene (505 nm), CH₂Cl₂ (516 nm), and CH₃CN

(521 nm). Compound 3 has a longer emission wavelength than that of 2, mainly due to the $\pi \cdots \pi$ stacking interactions between the anthracene moieties (Fig. 4).¹⁴





Fig. 5 Solid-state fluorescence spectra ($\lambda = 380$ nm) of 1–3 and their ground samples **1g**–**3g** at room temperature.

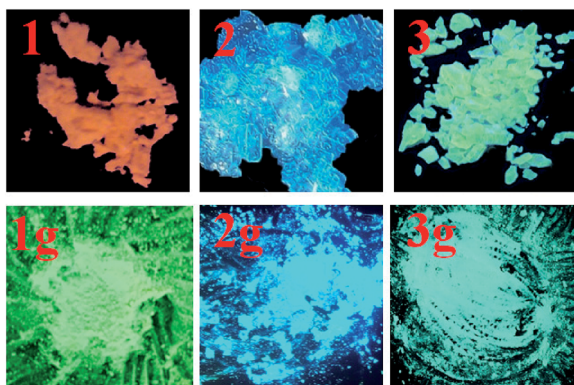


Fig. 6 Emission colors of 1–3 and their ground samples **1g**–**3g** at room temperature, under a lamp with 365 nm wavelength light.

In order to understand the different emission behaviors of 1–3, we performed quantum chemical calculations for the first dipole-allowed excited states in these compounds at the CAM-B3LYP/6-31G(d,p) level (the computational details are provided in the ESI[†]). The dominant natural transition orbitals (NTOs, Fig. S11[†]) show that the emission chromophore in each compound is mainly located at the anthracene moiety of the anbdtiH/anbdtiH₂⁺ molecule. In compound 2, the emission localizes at the central anbdtiH molecule because of the too weak π – π electronic coupling with other molecules, and, accordingly, this compound has the largest emission energy. On the contrary, the central molecules in both 1 and 3 show remarkable π – π electronic coupling with neighboring molecules, which may result in a red-shifted emission. It should be noted that the computational result of the intermolecular π – π electronic coupling in 1 is in agreement with the supramolecular chain structure showing a centroid–centroid distance of 3.765(1) Å between the two benzene rings from neighboring anthracene moieties (Fig. S9[†]). The NTOs for compound 1 are shown to be well distributed at the anthracene moieties of the central molecule and its two neighbors, while the NTOs for 3 can only delocalize over the central anbdtiH₂⁺ molecule and its

one nearest-neighbor molecule because the distance between the central molecule and its other neighbor is too large [the plane–plane distance between the two anthracene moieties is $\geq 6.991(1)$ Å in Fig. 3] to produce effective π – π electronic coupling. This may explain why compound 1 has a more significant red shift than 3.

After grinding, the stacking structure of 1 was destroyed, obtaining sample **1g**. This was confirmed by their different XRD patterns (Fig. S12[†]). Compared to 1, sample **1g** shows only a few broad and weak signals. As shown in Fig. 5 and 6, **1g** reveals a green emission at 520 nm, which is very similar to the emission of the anbdtiH monomolecule in CH₂Cl₂ (516 nm) (Fig. S10[†]). This suggests that neighboring anbdtiH molecules in **1g** have no obvious intermolecular (N–H)_{imidazole}⋯N_{imidazole} hydrogen bond interactions, such as those in 1. The destruction of the hydrogen bonds in 1 by grinding was further confirmed by the ATR IR spectra of 1 and **1g** (Fig. S13[†]). The spectra show obvious differences in the peaks around 840, 1140, 1382, 1431, 1560, 1974, and 2030 cm^{−1}. The different emission wavelengths of 1 and **1g** (603 nm vs. 520 nm) indicate that the connection of neighboring anbdtiH molecules through (N–H)_{imidazole}⋯N_{imidazole} hydrogen bonds could increase the intermolecular electronic coupling, thus resulting in the orange-red emission of 1. We measured the lifetimes of compound 1, and obtained $\tau_1 = 5.2$ ns (45.2% contribution) and $\tau_2 = 0.6$ ns (54.8% contribution) for the emission at 488 nm, $\tau_1 = 6.3$ ns (77.5% contribution) and $\tau_2 = 0.5$ ns (22.5% contribution) for the emission at 539 nm, and $\tau = 6.1$ ns for the emission at 603 nm. Compared to 1, the ground sample **1g** exhibits lifetimes of $\tau_1 = 5.1$ ns (49.9% contribution) and $\tau_2 = 1.3$ ns (50.1% contribution) for its emission at 520 nm. In addition, compounds 2 and 3 also exhibit emission-color changes upon grinding (Fig. 6) due to grinding-induced changes of the hydrogen bonds and/or π – π stacking interactions. Their emission-wavelength changes (red-shift of $\Delta\lambda = 20$ nm for 2, and blue-shift of $\Delta\lambda = 54$ nm for 3) are clearly smaller than that for 1 (blue-shift of $\Delta\lambda = 83$ nm) (Fig. 5, Table S3,† $\Delta\lambda$ calculation based on the maximum emission).

As shown in Fig. S14,† after heating at 110 °C for 10 minutes, sample **1g** could change its emission color from green to orange-red, indicating the formation of a new structure, namely **1gh**. A similar heating-induced structural transformation was also observed in the other anthracene derivative.^{6–8} The XRD pattern of **1gh** is different from that of 1 (Fig. S12[†]), which excludes the possibility of a heating-induced structural transformation from **1g** to 1. It should be noted that the emission bands of **1gh** (484, 533, and 604 nm) are very similar to those of 1 (488, 539, and 603 nm) (Fig. S15[†]). This suggests that neighboring anbdtiH molecules in **1gh** connect to each other through (N–H)_{imidazole}⋯N_{imidazole} hydrogen bonds. After grinding, **1gh** could switch its emission color from orange-red to green (Fig. S14[†]). We have not studied the influence of heating on the emission colors of **2g** and **3g** because they easily lost lattice CH₃OH and/or H₂O molecules upon heating. These lattice molecules are involved in hydrogen bond connections among anbdtiH/anbdtiH₂⁺ molecules. Their losses would complicate the structures and luminescence behaviors of the samples.



Clearly, the emission color of compound **1** could be reversibly switched between orange-red and green due to grinding-induced destruction and heating-induced formation of intermolecular (N–H)_{imidazole}⋯N_{imidazole} hydrogen bonds. It should be noted that compound **1** is significantly different to reported anthracene derivatives showing grinding- and heating-responsive luminescence behaviors,^{6–8} which have been described in the introduction. The emission-color switching in those compounds is mainly due to the regulation of intermolecular $\pi\cdots\pi$ stacking interactions between the anthracene moieties by grinding and heating. To the best of our knowledge, compared to those compounds, **1** is the first anthracene derivative where the intermolecular hydrogen bonds can be regulated by grinding and heating, thus resulting in reversible emission-color switching.

Considering the perfect face-to-face $\pi\cdots\pi$ stacking interactions between the anthracene moieties in compound **3** (Fig. 4), we studied its solid-state $[4\pi + 4\pi]$ photodimerization behavior. Since compound **3** has strong UV-vis absorption in the range of 200–450 nm (Fig. S16[†]), sunlight was used to irradiate its crystalline-phase sample (see the detail in the ESI[†]). After removing the unreacted sample, a white powder was obtained, namely **3-dimer**. Compounds **3** and **3-dimer** show significantly different UV-vis spectra (Fig. S17[†]). The former exhibits an intense absorption band at 255 nm, and the typical anthracene absorption bands at 351, 367 and 386 nm.¹⁵ The latter reveals a strong absorption band at 228 nm and a weak absorption band at 290 nm. In order to clarify the solid-state photodimerization behavior of **3**, we measured the crystal structure of **3-dimer**·2DMF. It crystallizes in the orthorhombic space group *Pbca*, and has a centrosymmetric molecular structure (Fig. 7). Two anbdtiH molecules connect to each other by C1–C8A and C8–C1A bonds [1.624(5) Å]. These distances are comparable to those in the dimer compound 1-(9-anthracenylmethyl)-3-ethylimidazolium iodide [1.636(4) Å].¹⁶ The central rings of the two original anthracene moieties lose their aromaticity and bend along the C1, C8 and C1A, C8A axes, respectively, forming the shape of flying wings. The dihedral angle between the two wings is 132.1(1)°. The two imidazole–thiophene moieties reach out roughly along the C1, C8 and C1A, C8A axes, respectively, forming a C8–C1–C15 angle of 164.755 (1)°. The two thiophene groups attached to each imidazole unit adopt an antiparallel conformation (Fig. S18[†]). In addition, the structure of **3-dimer**



Fig. 7 Molecular structure of **3-dimer**·2DMF. All H atoms attached to C atoms and the two lattice DMF molecules are omitted for clarity.

was also confirmed by its ¹H NMR spectrum (Fig. S2[†]). Our experimental results indicate that compound **3** could undergo a solid-state $[4\pi + 4\pi]$ photodimerization reaction upon irradiation with sunlight, forming **3-dimer**. In addition, compounds **1** and **2** have not shown solid-state $[4\pi + 4\pi]$ photodimerization behavior, which is in agreement with their packing structures not having face-to-face $\pi\cdots\pi$ stacking interactions between neighboring anthracene moieties.

Conclusions

We have synthesized a new anthracene derivative containing an imidazole unit, namely anbdtiH. Based on the molecular assembly of anbdtiH through intermolecular hydrogen bonds and/or $\pi\cdots\pi$ stacking interactions, compounds anbdtiH·CH₃Cl (**1**), anbdtiH·2CH₃OH (**2**) and anbdtiH₂·CF₃COO·CH₃OH·H₂O (**3**) have been prepared, which show distinct packing structures, and different luminescence and photodimerization behaviors. Compound **1** shows a supramolecular left-handed chiral chain structure, where neighboring anbdtiH molecules connect to each other through (N–H)_{imidazole}⋯N_{imidazole} hydrogen bonds. In contrast, neighboring anbdtiH/anbdtiH₂⁺ molecules in **2** and **3** are separated by solvent molecules and counter ions (CH₃OH, H₂O, and CF₃COO[−]), and are linked through hydrogen bonds to form a supramolecular chain structure and layer structure, respectively. In addition, compound **3** shows face-to-face $\pi\cdots\pi$ stacking interactions between interlayer anthracene moieties. Compounds **1–3** reveal an orange-red emission at 603 nm, a blue emission at 453 nm, and a green emission at 533 nm, respectively. These emissions can be evidently changed by grinding, resulting in a blue-shift of $\Delta\lambda = 83$ nm for **1**, a red-shift of $\Delta\lambda = 20$ nm for **2**, and a blue-shift of $\Delta\lambda = 54$ nm for **3**, because of the variation in intermolecular hydrogen bonds and/or $\pi\cdots\pi$ stacking interactions. Compared to the regulation of $\pi\cdots\pi$ stacking interactions between anthracene moieties by a grinding–heating process,^{6–8} compound **1** is the first anthracene derivative where the intermolecular (N–H)_{imidazole}⋯N_{imidazole} hydrogen bonds can be reversibly changed by grinding and heating, thus resulting in emission-color switching between orange-red and green. In addition, compound **3** is photoactive due to the perfect face-to-face $\pi\cdots\pi$ stacking between anthracene moieties. Thus, its solid-state $[4\pi + 4\pi]$ photodimerization results in compound **3-dimer**. Our experimental results demonstrate that the molecular stacking mode of anbdtiH can be purposefully modified by hydrogen bonds and/or $\pi\cdots\pi$ stacking interactions, thus obtaining the expected luminescence and/or photodimerization behaviors.

Acknowledgements

We thank the financial support from the NSF of Jiangsu province China (BK 20141314), the NSF of China (No. 21171090), the NSF of China - Royal Society of UK International Exchanges Scheme - Cost Share Program (No. 21411130119) and the National Science Fund for Talent Training in Basic Science (No. J1103310).



Notes and references

- 1 (a) S.-J. Yoon and S. Y. Park, *J. Mater. Chem.*, 2011, **21**, 8388; (b) F. Li, N. Gao, H. Xu, W. Liu, H. Shang, W. Yang and M. Zhang, *Chem.-Eur. J.*, 2014, **20**, 9991 and references therein.
- 2 (a) S. Yagai, S. Okamura, Y. Nakano, M. Yamauchi, K. Kishikawa, T. Karatsu, A. Kitamura, A. Ueno, D. Kuzuhara, H. Yamada, T. Seki and H. Ito, *Nat. Commun.*, 2014, **5**, 5013; (b) G. Fan and D. Yan, *Sci. Rep.*, 2014, **4**, 4933; (c) M.-S. Yuan, D.-E. Wang, P. Xue, W. Wang, J.-C. Wang, Q. Tu, Z. Liu, Y. Liu, Y. Zhang and J. Wang, *Chem. Mater.*, 2014, **26**, 2467.
- 3 (a) L. R. MacGillivray, G. S. Papaefstathiou, T. Friscic, T. D. Hamilton, D.-K. Bucar, Q. Chu, D. B. Varshney and I. Georgiev, *Acc. Chem. Res.*, 2008, **41**, 280; (b) Y. Ishida, A. S. Achalkumar, S. Kato, Y. Kai, A. Misawa, Y. Hayashi, K. Yamada, Y. Matsuoka, M. Shiro and K. Saigo, *J. Am. Chem. Soc.*, 2010, **132**, 17435; (c) K. M. Hutchins, J. C. Sumrak and L. R. MacGillivray, *Org. Lett.*, 2014, **16**, 1052.
- 4 (a) Z. Fei, N. Kocher, C. J. Mohrschladt, H. Ihmels and D. Stalke, *Angew. Chem., Int. Ed.*, 2003, **42**, 783; (b) A. N. Sokolov, T. Friscic and L. R. MacGillivray, *J. Am. Chem. Soc.*, 2006, **128**, 2806; (c) X.-F. Fu, Y.-F. Yue, R. Guo, L.-L. Li, W. Sun, C.-J. Fang, C.-H. Xu and C.-H. Yan, *CrystEngComm*, 2009, **11**, 2268; (d) Z. Zhang, Y. Zhang, D. Yao, H. Bi, I. Javed, Y. Fan, H. Zhang and Y. Wang, *Cryst. Growth Des.*, 2009, **9**, 5069; (e) Y. Mizobe, T. Hinoue, A. Yamamoto, I. Hisaki, M. Miyata, Y. Hasegawa and N. Tohnai, *Chem.-Eur. J.*, 2009, **15**, 8175; (f) T. Hinoue, M. Miyata, I. Hisaki and N. Tohnai, *Angew. Chem., Int. Ed.*, 2012, **51**, 155; (g) Y.-X. Li, H.-B. Zhou, J.-L. Miao, G.-X. Sun, G.-B. Li, Y. Nie, C.-L. Chen, Z. Chen and X.-T. Tao, *CrystEngComm*, 2012, **14**, 8286; (h) J. Zhang, J. Chen, B. Xu, L. Wang, S. Ma, Y. Dong, B. Li, L. Ye and W. Tian, *Chem. Commun.*, 2013, **49**, 3878; (i) M. Sugino, K. Hatanaka, Y. Araki, I. Hisaki, M. Miyata and N. Tohnai, *Chem.-Eur. J.*, 2014, **20**, 3069.
- 5 S. S. Babu, V. K. Praveen and A. Ajayaghosh, *Chem. Rev.*, 2014, **114**, 1973.
- 6 Z. Zhang, D. Yao, T. Zhou, H. Zhang and Y. Wang, *Chem. Commun.*, 2011, **47**, 7782.
- 7 (a) Y. Dong, B. Xu, J. Zhang, X. Tan, L. Wang, J. Chen, H. Lv, S. Wen, B. Li, L. Ye, B. Zou and W. Tian, *Angew. Chem., Int. Ed.*, 2012, **51**, 10782; (b) Y. Dong, J. Zhang, X. Tan, L. Wang, J. Chen, B. Li, L. Ye, B. Xu, B. Zou and W. Tian, *J. Mater. Chem. C*, 2013, **1**, 7554.
- 8 R. Li, S. Xiao, Y. Li, Q. Lin, R. Zhang, J. Zhao, C. Yang, K. Zou, D. Li and T. Yi, *Chem. Sci.*, 2014, **5**, 3922.
- 9 (a) F. Cicogna, G. Ingrosso, F. Lodato, F. Marchetti and M. Zandomenighi, *Tetrahedron*, 2004, **60**, 11959; (b) I. Zouev, T. Lavy and M. Kaftory, *Eur. J. Org. Chem.*, 2006, 4164; (c) M. Horiguchi and Y. Ito, *J. Org. Chem.*, 2006, **71**, 3608; (d) I. Zouev, D.-K. Cao, T. V. Sreevidya, M. Telzhensky, M. Botoshansky and M. Kaftory, *CrystEngComm*, 2011, **13**, 4376; (e) L. Zhu, A. Agarwal, J. Lai, R. O. Al-Kaysi, F. S. Tham, T. Ghaddar, L. Mueller and C. J. Bardeen, *J. Mater. Chem.*, 2011, **21**, 6258.
- 10 (a) M. Irie, T. Fukaminato, T. Sasaki, N. Tamai and T. Kawai, *Nature*, 2002, **420**, 759; (b) S. Kobatake, S. Takami, H. Muto, T. Ishikawa and M. Irie, *Nature*, 2007, **446**, 778; (c) T. Mutai, H. Satou and K. Araki, *Nat. Mater.*, 2005, **4**, 685; (d) A. Kishimura, T. Yamashita, K. Yamaguchi and T. Aida, *Nat. Mater.*, 2005, **4**, 546; (e) S. Srinivasan, P. A. Babu, S. Mahesh and A. Ajayaghosh, *J. Am. Chem. Soc.*, 2009, **131**, 15122.
- 11 C. Janiak, *J. Chem. Soc., Dalton Trans.*, 2000, 3885.
- 12 (a) M. O'Donnell, *Nature*, 1968, **218**, 460; (b) H. Bouas-Laurent, A. Castellan, J.-P. Desvergne and R. Lapouyade, *Chem. Soc. Rev.*, 2000, **29**, 43.
- 13 (a) J. Yang, D. Seneviratne, G. Arbatin, A. M. Andersson and J. C. Curtis, *J. Am. Chem. Soc.*, 1997, **119**, 5329; (b) D. A. Williamson and B. E. Bowler, *J. Am. Chem. Soc.*, 1998, **120**, 10902; (c) G. Canzi, J. C. Goeltz, J. S. Henderson, R. E. Park, C. Maruggi and C. P. Kubiak, *J. Am. Chem. Soc.*, 2014, **136**, 1710.
- 14 H. Zhang, Z. Zhang, K. Ye, J. Zhang and Y. Wang, *Adv. Mater.*, 2006, **18**, 2369.
- 15 (a) H. Bouas-Laurent, A. Castellan, J.-P. Desvergne and R. Lapouyade, *Chem. Soc. Rev.*, 2000, **29**, 43; (b) M. Kercher, B. Konig, H. Zieg and L. D. de Cola, *J. Am. Chem. Soc.*, 2002, **124**, 11541.
- 16 Q.-X. Liu, H.-B. Song, F.-B. Xu, Q.-S. Li and Z.-Z. Zhang, *Acta Crystallogr., Sect. E: Struct. Rep. Online*, 2004, **60**, o674.

