

CrossMark  
click for updatesCite this: *Chem. Sci.*, 2016, 7, 510

# Asymmetric supercapacitors with high energy density based on helical hierarchical porous $\text{Na}_x\text{MnO}_2$ and $\text{MoO}_2$ †

Xue-Feng Lu, Zhi-Xiang Huang, Ye-Xiang Tong and Gao-Ren Li\*

Helical hierarchical porous  $\text{Na}_x\text{MnO}_2/\text{CC}$  and  $\text{MoO}_2/\text{CC}$ , which are assembled from nanosheets and nanoparticles, respectively, are fabricated using a simple electrodeposition method. These unique helical porous structures enable electrodes to have a high capacitance and an outstanding cycling performance. Based on the helical  $\text{Na}_x\text{MnO}_2/\text{CC}$  as the positive electrodes and helical  $\text{MoO}_2/\text{CC}$  as the negative electrodes, high performance  $\text{Na}_x\text{MnO}_2/\text{CC}//\text{MoO}_2/\text{CC}$  asymmetric supercapacitors (ASCs) are successfully assembled, and they achieve a maximum volume  $C_{\text{sp}}$  of  $2.04 \text{ F cm}^{-3}$  and a maximum energy density of  $0.92 \text{ mW h cm}^{-3}$  for the whole device and an excellent cycling stability with 97.22%  $C_{\text{sp}}$  retention after 6000 cycles.

Received 3rd September 2015

Accepted 6th October 2015

DOI: 10.1039/c5sc03326h

www.rsc.org/chemicalscience

## 1. Introduction

Increasing demands in portable electronics and future green transportation are pushing the research towards electrochemical energy storage (EES) systems with high energy density, high power density and long cycling life.<sup>1</sup> Electrochemical capacitors, also known as supercapacitors, bridge the gap between batteries and conventional capacitors in terms of their high power density and have been regarded as the most promising EES devices.<sup>2</sup> However, their energy density is still relatively low, which has restricted their potential applications. Therefore, the improvement of energy density is crucial for supercapacitors to meet future energy demands.

As we know, the energy density of a supercapacitor device can be calculated according to the equation  $E = 1/2 C_{\text{sp}} V^2$ , and it can be enhanced by maximizing the specific capacitance ( $C_{\text{sp}}$ ) and operation voltage ( $V$ ).<sup>3</sup> The promising approach for the enhancement of  $C_{\text{sp}}$  is to develop new electrodes with high  $C_{\text{sp}}$  values.<sup>4</sup> An effective approach to increase the operation voltage is to use an organic electrolyte, which can provide a wide voltage window up to 3.0 V. However, they suffer from high cost, poor ionic conductivity and high toxicity, which limit their wide application. In addition, a promising alternative for increasing the operation voltage is to develop asymmetric supercapacitors (ASCs), which typically consist of cathodes as the energy source and anodes as the power source.<sup>5</sup> Compared with symmetric supercapacitors, the ASCs

take advantage of the different voltage windows of two electrodes in the same electrolyte to increase the device operating voltage and thus significantly improve the energy density. In recent decades, intensive efforts have been devoted to explore various ASCs, such as H-TiO<sub>2</sub>@MnO<sub>2</sub>//H-TiO<sub>2</sub>@C (1.8 V),<sup>4</sup> ZnO@MnO<sub>2</sub>//rGO (1.8 V),<sup>6</sup> Ni/NiO//rGO (1.5 V),<sup>7</sup> and NiCo<sub>2</sub>O<sub>4</sub>//active carbon (1.5 V).<sup>8</sup> Most ASCs use carbon-based materials as negative electrodes because of their large surface area, excellent electrical conductivity and outstanding stability.<sup>9</sup> However, the low  $C_{\text{sp}}$  of carbon materials severely limits the energy density of the SCs according to the equation of  $1/C = 1/C_{\text{an}} + 1/C_{\text{cat}}$  ( $C_{\text{an}}$ : capacitance of the anode;  $C_{\text{cat}}$ : capacitance of the cathode). In this regard, some new negative electrodes with high  $C_{\text{sp}}$  values, such as MoO<sub>3</sub>,<sup>3a,10</sup> Fe<sub>2</sub>O<sub>3</sub>,<sup>11</sup> and some metal nitrides<sup>12</sup> have been developed for ASCs. But due to the narrow voltage window, the unbalanced capacity between the cathode and anode electrodes and the unsatisfactory cycling stability of metal oxide negative electrodes, it is still a huge challenge to achieve ASCs with high energy and power densities.

Based on the above considerations, in this paper we designed and synthesized helical hierarchical porous  $\text{Na}_x\text{-MnO}_2$  and  $\text{MoO}_2$  on carbon cloth (CC) as the positive and negative electrodes, respectively, for ASCs. Manganese oxides have been widely thought to be the most promising material because of their low cost, high abundance, large theoretical  $C_{\text{sp}}$ , and environmental friendliness.<sup>13</sup> As a polymorph of MnO<sub>2</sub>, the sodium-birnessite-type MnO<sub>2</sub> ( $\text{Na}_x\text{MnO}_2$ ) has a two-dimensional layer-structure with bicontinuous networks of solids and pores,<sup>14</sup> and it is an attractive candidate for ASCs as a positive electrode material. MoO<sub>2</sub> as a negative electrode was investigated because of its rich chemistry associated with multiple valence states, low electrical resistivity, natural

MOE Laboratory of Bioinorganic and Synthetic Chemistry, KLGHEI of Environment and Energy Chemistry, School of Chemistry and Chemical Engineering, Sun Yat-sen University, Guangzhou 510275, China. E-mail: ligaoren@mail.sysu.edu.cn

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c5sc03326h




abundance, and affordable cost.<sup>15</sup> The unique helical hierarchical porous structure of Na<sub>x</sub>MnO<sub>2</sub> was assembled from nanosheets and that of MoO<sub>2</sub> was assembled from mesoporous nanoparticles. The helix is a fantastic yet ubiquitous geometry in nature, science, art and architecture, and it exhibits distinctive mechanical, chemical, and physical properties.<sup>16</sup> When a helical structure is used in electrodes for supercapacitors, the appropriate spiral distance and diameter are in favor of electrolyte insertion and thus will improve the utilization ratio of the active material. The interspace between two pitches can serve as an “ion reservoir” and further improve the cycling stability of the electrodes. The hierarchical porous structure will be much less vulnerable to dissolution, Ostwald ripening and aggregation, and will provide a large surface area and fast electrolyte penetration/diffusion. Besides, the hierarchical porous structure can also buffer the volume change well, avoiding the structural collapse of the electrodes during the charge/discharge process. The electrochemical measurements demonstrate that the helical hierarchical porous Na<sub>x</sub>MnO<sub>2</sub> shows a maximal areal capacitance of 329.69 mF cm<sup>-2</sup> with a potential window of 0–1.0 V and the helical hierarchical porous MoO<sub>2</sub> shows a maximal areal C<sub>sp</sub> of 174.97 mF cm<sup>-2</sup> with a potential window of –1.1–0 V. The ASC device was assembled based on the helical hierarchical porous Na<sub>x</sub>MnO<sub>2</sub>/CC as the positive electrode and helical hierarchical porous MoO<sub>2</sub>/CC as the negative electrode, and it shows a high volume C<sub>sp</sub> of 2.04 F cm<sup>-3</sup> and a high energy density of 0.92 mW h cm<sup>-3</sup> based on the whole device. Meanwhile, such an ASC device exhibits a high cycling life with 97.22% C<sub>sp</sub> retention after 6000 cycles. The present encouraging findings will open up a new opportunity for the development of ASCs with high energy and power densities.


## 2. Experimental section

### Preparation of electrode materials

All the chemical reagents used in this study were of analytical grade (AR). Electrodeposition was carried out in a simple two-electrode cell *via* galvanostatic electrolysis and a graphite electrode was used as a counter electrode (spectral grade). Carbon cloth was used as the working electrode for the electrodeposition and it was washed with ethanol and water successively in an ultrasonic bath for 5 min. The helical Na<sub>x</sub>MnO<sub>2</sub> was electrodeposited on the carbon cloth in a 15 mL solution of 0.02 M Mn(CH<sub>3</sub>COO)<sub>2</sub> + 0.2 M Na<sub>2</sub>SO<sub>4</sub> at a current density of 4.0 mA cm<sup>-2</sup> on the anode at room temperature for 10 min. The electrodeposition process is expressed as follows:<sup>14,19</sup>



The helical MoO<sub>2</sub> was electrodeposited in a 15 mL solution of 0.01 M (NH<sub>4</sub>)<sub>6</sub>Mo<sub>7</sub>O<sub>24</sub> at a current density of 4.0 mA cm<sup>-2</sup> on the cathode at room temperature for 30 min followed by an annealing process in an NH<sub>3</sub> atmosphere. The electrodeposition process is expressed as follows:



### Fabrication of ASCs

The ASC device was assembled using the helical Na<sub>x</sub>MnO<sub>2</sub>/CC as the positive electrode and helical MoO<sub>2</sub>/CC as the negative electrode with a separator (NKK separator; Nippon Kodoshi Corporation, Kochi, Japan) between the two electrodes. A Na<sub>2</sub>SO<sub>4</sub> aqueous solution (1.0 M) was used as the electrolyte. To avoid leakage of the electrolyte, the entire device was sealed by two pieces of PET membrane with a small part of the electrode kept outside.

### Material characterizations and electrochemical measurements

The morphologies, microstructures and compositions of the products were characterized using field-emission scanning electron microscopy (FE-SEM, JSM-6330F), X-ray diffraction (XRD, D-MAX 2200 VPC), transmission electron microscopy (TEM, Tecnai™ G2 F30), and X-ray photoelectron spectroscopy (XPS, ESCALab250). Inductively coupled plasma atomic emission spectroscopy (ICP, SPECTRO) was used to analyze the loading of the active materials. The electrochemical measurements of the electrodes were carried out in a standard three-electrode electrolytic cell in 1.0 M Na<sub>2</sub>SO<sub>4</sub> aqueous solution. A graphite electrode was used as the counter electrode. A saturated calomel electrode (SCE) was used as the reference electrode. The cyclic voltammetry and chronopotentiometric measurements were performed using a CHI 760E electrochemical workstation (CH instruments, Inc.) to determine the electrochemical properties. EIS was conducted in the frequency range between 0.01 Hz and 100 kHz with an amplitude of 5 mV at the open-circuit potential.

## 3. Results and discussion

As shown in Scheme 1, the electrodeposition method was used to fabricate the helical hierarchical porous Na<sub>x</sub>MnO<sub>2</sub> and MoO<sub>2</sub>, which were directly grown on carbon cloth without a binder (the details are described in the Experimental section). SEM images of Na<sub>x</sub>MnO<sub>2</sub> with different magnifications are shown in Fig. 1a and S1a,† which show the perfect and uniform helical structures grown on carbon fibers. More interestingly, the magnified SEM image in Fig. 1b shows that the helical structures consist of nanosheets. The thickness of these nanosheets is 15–20 nm. TEM images of Na<sub>x</sub>MnO<sub>2</sub> are shown in Fig. 1c and S1b,† which clearly show the porous structures. The HRTEM image in Fig. 1d shows the lattice spacings of 0.697, 0.349 and 0.252 nm, which correspond to (001), (002) and (100) crystal planes of Na<sub>x</sub>MnO<sub>2</sub>, respectively.<sup>17</sup> The SAED pattern in the inset of Fig. 1c also shows the polycrystalline structure of Na<sub>x</sub>MnO<sub>2</sub>. A cross-sectional SEM image in Fig. S2† shows that the thickness of the helical microstructures is ~1.0 μm. The surface electronic state and chemical composition of the helical Na<sub>x</sub>MnO<sub>2</sub> was





Scheme 1 Representation of the fabrication of the helical hierarchical porous  $\text{Na}_x\text{MnO}_2/\text{CC}$  and  $\text{MoO}_2/\text{CC}$ .

examined using an XPS spectrum. The XPS survey spectrum of the helical  $\text{Na}_x\text{MnO}_2$  is shown in Fig. S3,<sup>†</sup> which shows the existence of the elements Mn, O, Na and C. The signals of C come from the carbon cloth substrate. The atomic ratio of Na/Mn is about 0.2, which is confirmed using energy dispersive X-ray spectroscopy (EDX) as shown in Fig. S4.<sup>†</sup> In the Mn 2p spectra (Fig. 1e), two kinds of manganese species containing  $\text{Mn}^{3+}$  and  $\text{Mn}^{4+}$  can be observed. The fitting peaks at 641.45 eV and 653.15 eV are indexed to  $\text{Mn}^{3+}$ , while the fitting peaks at 642.61 eV and 654.31 eV are indexed to  $\text{Mn}^{4+}$ .<sup>18</sup> Additionally, the Mn 3s peaks are useful for determining the oxidation state of

Mn. In Fig. 1f, the energy separation between the two peaks of Mn 3s is 4.8 eV, which corresponds to an average Mn oxidation state of  $\sim 3.8$  according to a linear relationship between the oxidation state of manganese and the  $\Delta E$  value.<sup>18,19</sup> The atomic ratio of  $\text{Mn}^{3+}/\text{Mn}^{4+}$  in the sample is about 1/4. The O 1s spectrum shown in Fig. 1g is deconvoluted into three components. The bands at 529.9, 531.3 and 533.1 eV can be assigned to the oxygen bonds of Mn–O–Mn, Mn–O–H and H–O–H, respectively.<sup>19</sup> The bond of Mn–O–Mn comes from  $\text{Na}_x\text{MnO}_2$  and those of Mn–O–H and H–O–H can be attributed to the adsorbed  $\text{H}_2\text{O}$  or crystal  $\text{H}_2\text{O}$ . Based on the above results, the composition of

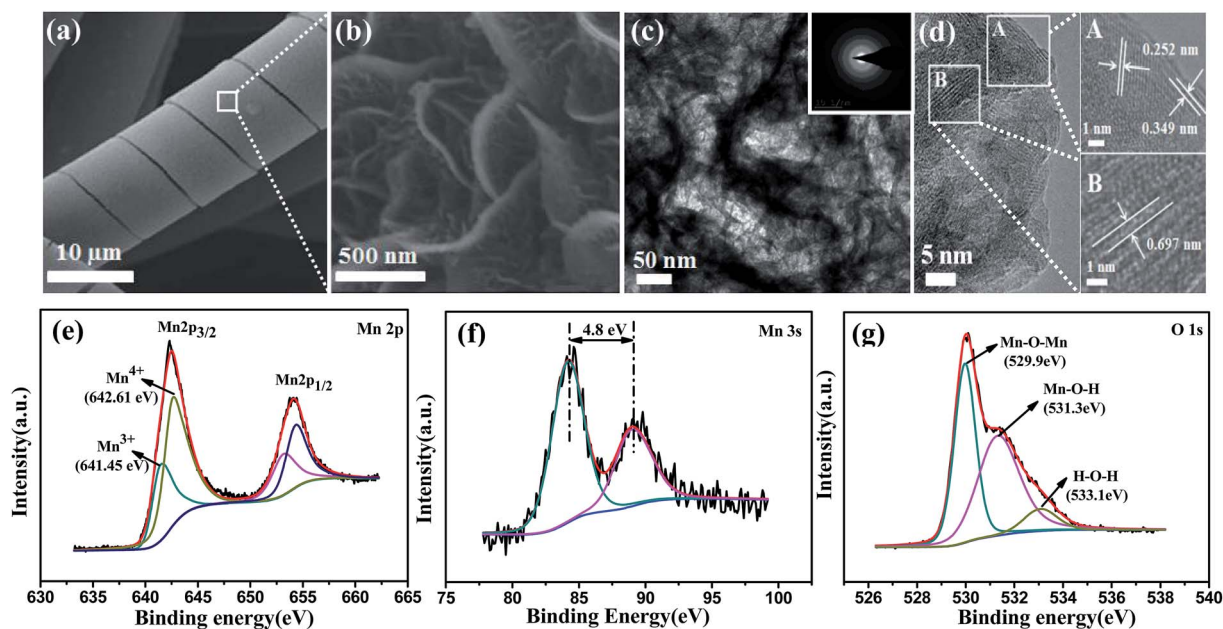


Fig. 1 (a and b) SEM images of the helical  $\text{Na}_x\text{MnO}_2$  with hierarchical porous structures; (c) TEM and (d) HRTEM images of the typical  $\text{Na}_x\text{MnO}_2$  nanosheets (inset in (c) is the SAED pattern); XPS spectra of the helical  $\text{Na}_x\text{MnO}_2$  of (e) Mn 2p, (f) Mn 3s, and (g) O 1s.







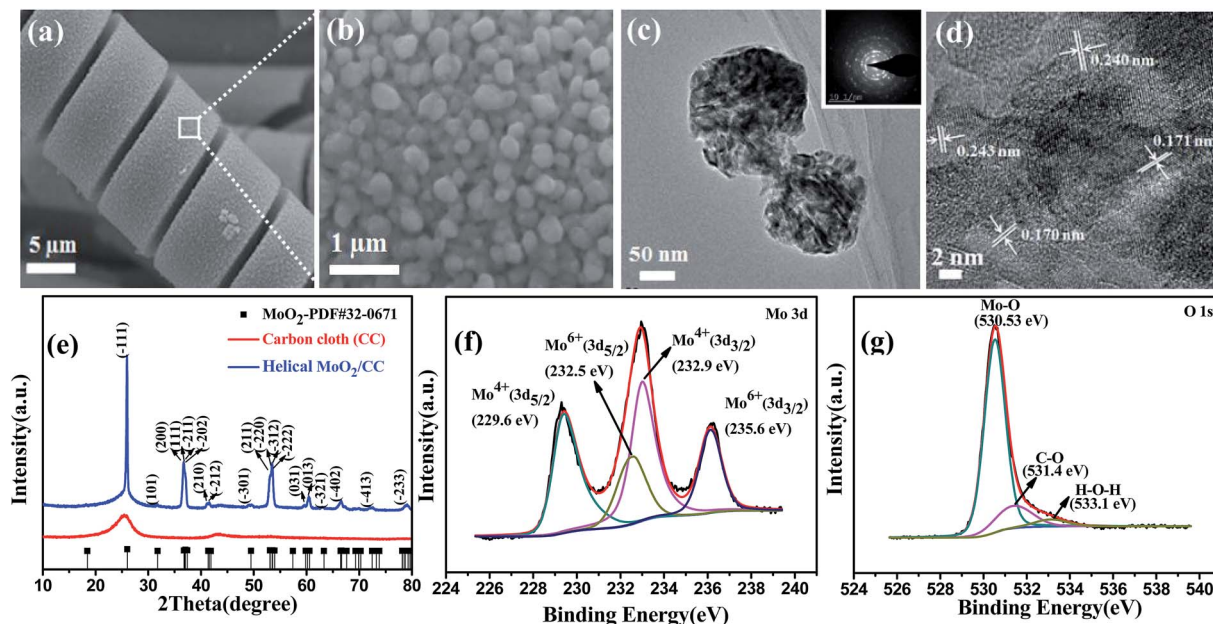


Fig. 3 (a and b) SEM images of the helical  $\text{MoO}_2$  with different magnifications; (c) the TEM image of  $\text{MoO}_2$  nanoparticles (inset is the SAED pattern); (d) the HRTEM image of the helical  $\text{MoO}_2$ ; (e) XRD patterns of the helical  $\text{MoO}_2/\text{CC}$  and CC; XPS spectra of the helical  $\text{MoO}_2/\text{CC}$ : (f) Mo 3d and (g) O 1s.

$\text{MoO}_2$  in air.<sup>24,25</sup> The XPS spectrum of O 1s is shown in Fig. 3g, which shows that the main peak at 530.53 eV can be assigned to the Mo–O bond. The bands of 531.4 and 533.1 eV correspond to C–O and O–H bonds, respectively,<sup>24,25</sup> and they can be attributed to the adsorbed  $\text{H}_2\text{O}$  on the carbon cloth.

The fabricated helical  $\text{MoO}_2/\text{CC}$  electrode possesses a perfect capacitance behavior with a wide potential window of  $-1.1$ – $0$  V (vs. SCE) in a solution of  $1.0$  M  $\text{Na}_2\text{SO}_4$ . The wide potential window may be the result of the high overpotential of  $\text{H}_2$  and  $\text{O}_2$  evolution, which is related to the structure and properties of the electrode material.<sup>26</sup> Fig. 4a and b show the CV and GCD curves of the helical  $\text{MoO}_2/\text{CC}$ , respectively, which are symmetric and linear, respectively, without an obvious IR drop, indicating a good capacitance performance. As shown in Fig. 4c, the highest areal  $C_{\text{sp}}$  obtained from the GCD curves is  $174.97$  mF  $\text{cm}^{-2}$  at a current density of  $1.43$  mA  $\text{cm}^{-2}$ , which is much larger than those of other metal oxide/nitride negative electrodes, such as  $\alpha$ - $\text{Fe}_2\text{O}_3$ ,<sup>27</sup>  $\text{MoO}_3$ ,<sup>28a</sup> and VN.<sup>12a,28b</sup> The kinetic features of the helical  $\text{MoO}_2/\text{CC}$  electrode were further investigated by measuring the EIS spectrum as shown in Fig. 4d, which shows a small bulk solution resistance ( $R_s$ ) of  $7.5$   $\Omega$ ,<sup>29</sup> a small charge-transfer resistance ( $R_{\text{ct}}$ ) of  $0.5$   $\Omega$ , and fast ion diffusion into the  $\text{MoO}_2/\text{CC}$  electrode.<sup>30</sup> Moreover, the helical  $\text{MoO}_2/\text{CC}$  shows a high cycling stability with a  $C_{\text{sp}}$  retention of 91.62% after 5000 cycles as shown in Fig. S12.† To evaluate the change of charge-transfer resistance, we compared the EIS spectra of the helical  $\text{MoO}_2/\text{CC}$  before and after the cycling test as shown in Fig. S13,† from which we can see that the charge-transfer resistance of the electrode becomes a little bigger after 5000 cycles.

The flexible asymmetric supercapacitor (ASC) device was assembled using the helical  $\text{Na}_x\text{MnO}_2/\text{CC}$  as the positive

electrode and the helical  $\text{MoO}_2/\text{CC}$  as the negative electrode ( $\text{Na}_x\text{MnO}_2/\text{CC}/\text{MoO}_2/\text{CC}$  ASC). Fig. 5a shows the schematic structure of the  $\text{Na}_x\text{MnO}_2/\text{CC}/\text{MoO}_2/\text{CC}$  ASC, which is sealed by two thin pieces of PET membrane. Taking advantage of the different potential windows of the  $\text{Na}_x\text{MnO}_2/\text{CC}$  and  $\text{MoO}_2/\text{CC}$  electrodes (Fig. S14a†), the operating cell potential of the assembled ASCs is expected to be 2.1 V. However, a faradic reaction is observed in the CV and GCD curves beyond the potential of 1.8 V. As shown in Fig. S14b,† an oxidation peak is observed beyond 1.8 V, highlighted by a dashed box, which is also observed in the GCD curves (Fig. S14c†). When the ASC devices were tested in the potential windows of 2.0 and 2.1 V for 6000 cycles, their capacitance retention is only 63.01% and 40.25%, respectively, as shown in Fig. S14d.† However, when tested in a potential window of 1.8 V, the ASC has a good cycling stability with a much higher capacitance retention of 97.22%, which is significantly better than those reported in previous work (typically 70–85% retention over 1000 cycles).<sup>26a,32</sup>

Fig. 5b shows the CV curves of an optimized  $\text{Na}_x\text{MnO}_2/\text{CC}/\text{MoO}_2/\text{CC}$  ASC at different scan rates with a potential window of 0–1.8 V in  $1.0$  M  $\text{Na}_2\text{SO}_4$  electrolyte. These CV curves exhibit rectangular-like shapes, revealing an ideal capacitive behavior and fast charge/discharge properties. As shown in Fig. 5c, the GCD curves at different current densities are all reasonably symmetrical and show a good linear relationship of the charge/discharge voltage *versus* time particularly at a low current density. This result also indicates the ideal capacitive characteristics and the rapid charge/discharge properties of the assembled ASC device. The volumetric  $C_{\text{sp}}$  calculated using the discharging curves is shown in Fig. S15,† which shows the highest  $C_{\text{sp}}$  of  $2.04$  F  $\text{cm}^{-3}$  at  $0.57$  mA  $\text{cm}^{-2}$ . The  $C_{\text{sp}}$  of  $2.04$  F  $\text{cm}^{-3}$



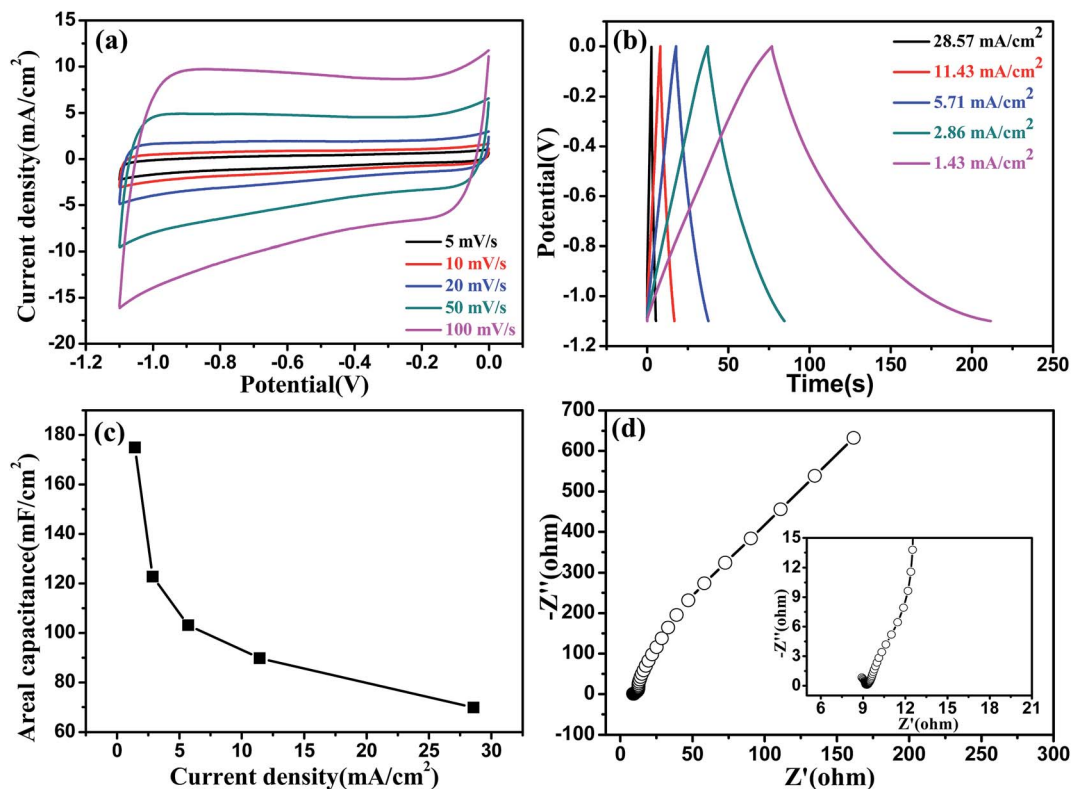


Fig. 4 (a) CV curves at different scan rates; (b) GCD curves at different current densities of the helical  $\text{MoO}_2$  in 1.0 M  $\text{Na}_2\text{SO}_4$  electrolyte; (c) areal capacitance calculated from GCD curves as a function of current densities; (d) EIS spectra of  $\text{MoO}_2$  (inset is the enlarged view of the high frequency region).

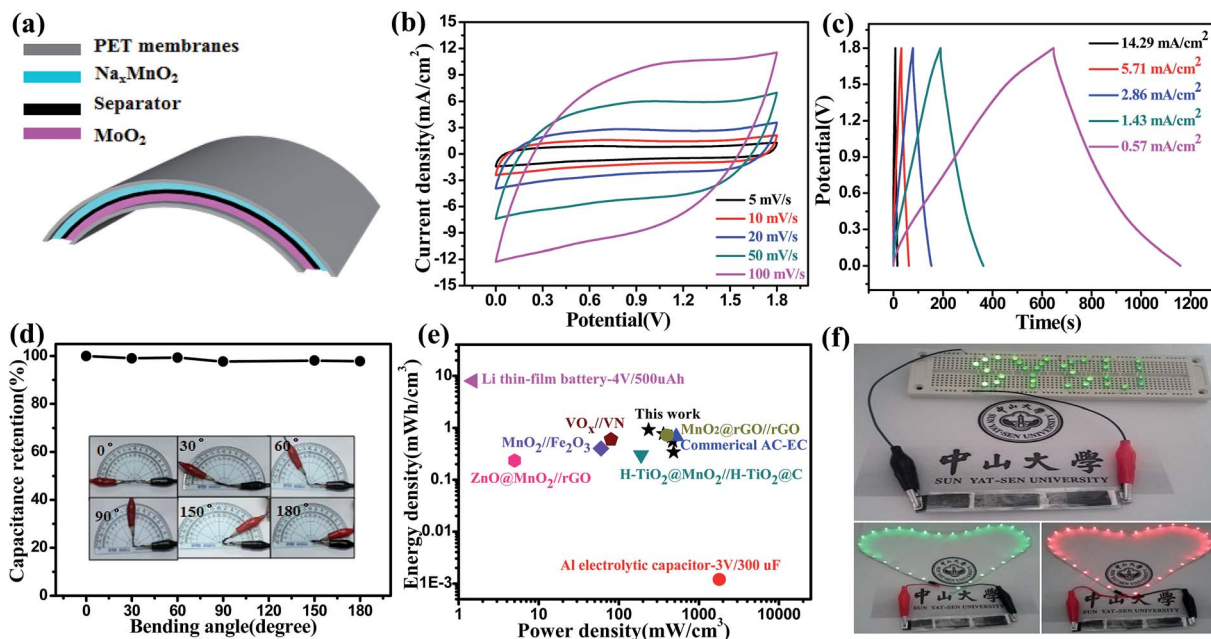


Fig. 5 (a) A schematic illustration of the structure of a flexible  $\text{Na}_x\text{MnO}_2/\text{CC} // \text{MoO}_2/\text{CC}$  ASC with two electrodes separated by the TF45 (NKK) membrane (separator); (b) CV curves of the ASC at different scan rates; (c) GCD curves of the ASC at different current densities; (d) stability performance of the ASC collected at different bending angles (the inset shows the flexibility under the different bending angles); (e) Ragone plots of the  $\text{Na}_x\text{MnO}_2/\text{CC} // \text{MoO}_2/\text{CC}$  ASC device. The values reported in the literature for other ASC devices are added for comparison; (f) a SYSU logo consisting of 32 green LEDs and a piece of green LED soft rope light powered by the assembled ASCs with three in series.







