

Cite this: *Nanoscale Adv.*, 2019, 1, 613

Porous tal palm carbon nanosheets: preparation, characterization and application for the simultaneous determination of dopamine and uric acid

A. J. Saleh Ahammad,^{ID}*^a Noyon Odhikari,[†]^a Syed Shaheen Shah,[†]^b
Md. Mahedi Hasan,^{ID}^a Tamanna Islam,^{ID}^a Poly Rani Pal,^a
Mohammed Ameen Ahmed Qasem^b and Md. Abdul Aziz^{*b}

A novel porous tal palm carbon nanosheet (PTPCN) material was synthesized from the leaves of *Borassus flabellifer* (tal palm) and used for developing an electrochemical sensor through modifying a glassy carbon electrode (GCE) simply by drop-casting on it a solution of the material for the sensitive simultaneous detection of dopamine (DA) and uric acid (UA), even in the presence of interfering species. The drop-casting solution was prepared by simply dispersing the PTPCNs in ethanol without using any other binding materials (e.g. Nafion). The surface morphologies of the PTPCNs were studied through field-emission scanning electron microscopy (FESEM), transmission electron microscopy (TEM) and high resolution TEM (HRTEM). Energy dispersive X-ray spectroscopy (EDS) and X-ray diffraction spectroscopy (XPS) studies revealed the chemical composition of the PTPCNs' surface. Their structural properties were studied using X-ray diffraction (XRD) and Raman spectroscopy. Brunauer–Emmett–Teller (BET) analysis confirmed the surface area and pore volume to be 1094.53 m² g⁻¹ and 0.74 cm³ g⁻¹, respectively, while Barrett–Joyner–Halenda (BJH) pore-size distribution showed the average pore size to be 22 nm. The sufficiently large surface area and pore-size distribution suggested better electrocatalytic properties compared to the average modifying materials. The modified electrode (PTPCNs/GCE) was characterized through impedimetric and CV techniques in standard potassium ferricyanide solution for evaluating their charge-transfer resistance and electrochemical properties. The limits of detection (S/N = 3) were 0.17 μM and 0.078 μM and the sensitivities were 1.2057 μA μM⁻¹ cm⁻² and 2.693 μA μM⁻¹ cm⁻² for UA and DA, respectively. The possible interactions that took place between the PTPCNs and the analytes that aided in the enhancement of the electroanalytical performance of the PTPCNs/GCE are discussed based on the experimental findings and established theoretical concepts. The PTPCNs/GCE was successfully employed for analyzing real samples, like dopamine injection and urine.

Received 14th July 2018
Accepted 3rd October 2018

DOI: 10.1039/c8na00090e

rsc.li/nanoscale-advances

1. Introduction

Dopamine (DA) is an organic catecholamine generally produced in the substantia nigra region of the central nervous system and serves as a neurotransmitter by means of sending signals from the midbrain to the other parts.¹ The midbrain DA is projected to almost all regions of the human brain, including the nucleus accumbens, dorsal striatum and cortical areas *via* dopaminergic pathways or neurons, each of which has different neuropsychiatric functions, including human cognition,

reward-motivated actions (desire, wanting, pleasure, etc.), motor nerve control as well as hormonal balance by controlling their release.^{2–4} Uric acid (UA), on the other hand, is an important natural antioxidant that primarily lessens the damage to neurons resulting from oxidative stress as well as DNA damage.⁵ Precursor metabolized purines form UA in the liver, intestine and muscles and exists mostly in urine, blood serum and brain tissue.⁶ Dysfunctions in the human body due to altered levels of DA and UA are linked to several health issues. For instance, Parkinson's, a neurodegenerative disease that causes motor disability, is the result of neuron death that hinders the generation of dopamine in the midbrain.⁷ It has been demonstrated that a reduced level of UA in the caudate of the midbrain accelerates DA oxidation, which eventually increases the risk of Parkinson's disease.⁷ Another neurological disorder, Alzheimer's, responsible for dementia and aging, is

^aDepartment of Chemistry, Jagannath University, Dhaka 1100, Bangladesh. E-mail: ajsahammad@chem.jnu.ac.bd; Fax: +880 2 7113713; Tel: +880 2 9583794

^bCenter of Research Excellence in Nanotechnology, King Fahd University of Petroleum and Minerals, Dhahran 31261, Saudi Arabia. E-mail: maziz@kfupm.edu.sa; Fax: +966-13-860-7264; Tel: +966-13-860-3744

[†] These authors contributed equally to this work.



with a particle size of ≤ 100 micron. A specific amount (2 g) of the collected fine powders were mixed with sodium bicarbonate (NaHCO_3) in a mortar and pestle with a mass ratio of 1 : 4. The uniformly mixed fine powders were carbonized in a tube furnace at 850°C for 5 h under a nitrogen atmosphere. The final products after carbonization were washed with 0.5 M HCl (two times), with DI water (three times), and then dried overnight at 60°C to obtain the PTPCNs. Scheme 1 shows the preparation process of the PTPCNs.


2.3. Electrode modification

Approximately 0.5 mg of PTPCNs was dispersed in 3 mL of ethanol solution by sonicating for half an hour. Once a uniformly dispersed solution was obtained, drop-casting was carried out using a micropipette. Before that, the GCE was polished thoroughly with a polishing cloth using $0.5\ \mu\text{m}$ slurry

of alumina. Any trace of the slurry was removed from the GCE by washing it with excess DI several times. Finally, we modified the GCE using $5\ \mu\text{L}$ of the dispersed solution through drop-casting and then dried it in the open air at room temperature. We used $5\ \mu\text{L}$ of the PTPCNs solution as this showed a minimum charging current and maximum response towards the analytes. The PTPCNs/GCE preparation process is shown in Scheme 2.

2.4. Instrumentation

FESEM (TESCAN LYRA 3, Czech Republic) was performed to obtain the FESEM images, with an Oxford Instruments Xmass detector equipped with the FESEM used for the energy dispersive X-ray spectra (EDS). Transmission electron microscopy (TEM) (JEM-2011; JEOL) was used to obtain the TEM images. A iHR320 with CCD detector, HORIBA, Raman spectrometer equipped with green laser (300 mW), excitation wavelength $\lambda_0 =$

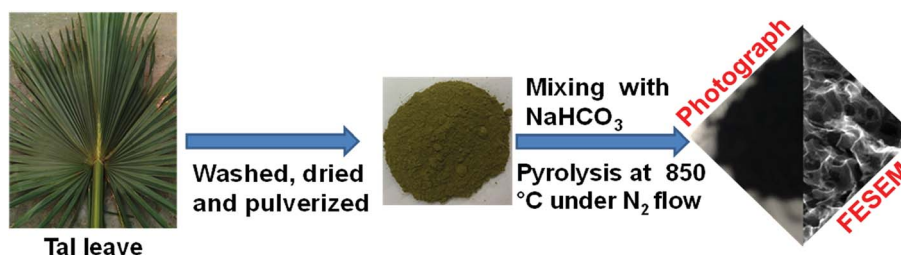

Scheme 1 Schematic representation for the preparation of PTPCNs from tal leaves at 850°C .



Scheme 2 Schematic representation of the procedure used to prepare the PTPCNs/GCE and its electrochemical response to DA and UA.



532 nm, was used for the study and detection of the graphite structure in the synthesized materials. X-ray diffraction analysis and chemical analysis of the prepared porous carbon nanosheets were achieved by means of a high-resolution Rigaku Ultima IV X-ray diffractometer equipped with Cu-K (α) radiation, and an XPS equipped with an Al K-alpha micro-focusing X-ray monochromator (ESCALAB 250Xi XPS Microprobe, Thermo Scientific, USA), respectively. Micromeritics ChemiSorb 2750 was used for the BET and BJH Analysis to measure the surface area and pore size of the porous carbon nanosheets. A Power Sonic 603 ultrasonic cleaner was used for sonication. All the voltammetric and impedimetric experiments were done on a single potentiostat (CHI 660E instrument, USA). Bare GCE and PTPCNs/GCE as the working electrode, Ag/AgCl (3 M KCl) as the reference electrode and Pt wire as the counter electrode were utilized for the three electrode system.

3. Results and discussions

3.1. Characterization of the PTPCNs

Fig. 1(A–C) show the FESEM morphology of carbon prepared from tal palm leaves. These FESEM micrographs show that the as-prepared sample consisted of interconnected nanosheet structures. Fig. 1(B) and (C) clearly indicate a very regular nanosheet structure interconnected with each other with numerous pores. These well-organized interconnected porous carbon nanosheets are useful for the fast diffusion of an electrolyte throughout the electrochemical sensing applications. Fig. 1(D) shows the corresponding EDS spectrum, obtained from the indicated position of Fig. 1(B). These results show the presence of a pure elemental composition of carbon and oxygen

only. The presence of extra elements, Sn and Si, in the EDS spectrum were due the fluorine doped tin oxide (FTO)-coated glass used as a substrate for the sample preparation of the EDS analysis.

The carbon nanosheets with a porous morphology were further characterized by transmission electron microscopy (TEM). Fig. 2(A) shows the low magnified TEM image, which reveals the architecture of the interconnected nanosheets, which clearly highlight the huge amounts of channels and pores. Furthermore, large quantities of mesopores can be clearly observed in Fig. 2(B). These carbon nanosheets with interconnected properties and a porous nature can provide a promising route for sensing applications due to the easily diffusion of electrolyte ions. This behaviour is significant for fast ion transfer in sensing applications.²⁵

Fig. 3(A) shows the Raman spectrum of the porous carbon phase, which is composed of two peaks: the first peak in the range of 1580 to 1620 cm^{-1} , called the G-band, and the second peak in the range of 1320 to 1360 cm^{-1} , called the D-band. These bands appear from the sp^2 hybridized carbon structure and are related to graphitic carbon. The obtained $I_{\text{D}}/I_{\text{G}}$ (I_{D} signifies the intensity of the D band and I_{G} denotes the intensity of the G band) was 0.933. This high intensity ratio indicated the presence of a significant amount of disordered carbon in the prepared porous carbon nanosheets. The physical properties of carbon nanosheets are mainly dependent on C to C bonds.⁸ Fig. 3(B) shows the XRD pattern of the porous carbon nanosheets prepared from tal palm leaves at 850 $^{\circ}\text{C}$. The broad diffraction peak occurring in the 2θ range of 14 $^{\circ}$ to 33 $^{\circ}$ can be attributed to the typical activated carbon/amorphous carbon structure.²⁶ However, a tiny and sharp peak at $\sim 23^{\circ}$ on top of the

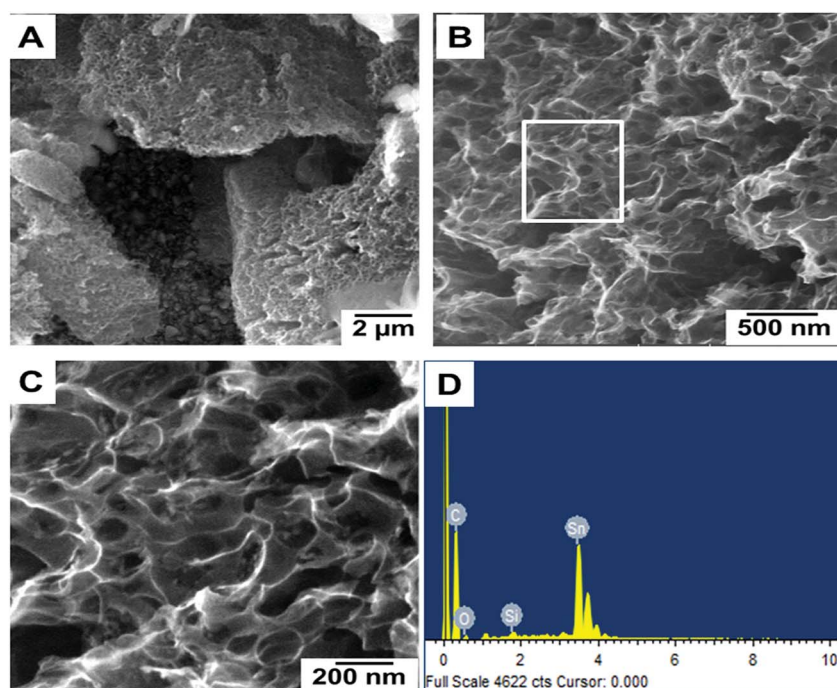


Fig. 1 Different magnified FESEM images (A–C) of carbon nanosheets prepared from tal palm leaves. (D) is the corresponding EDS spectrum recorded from the white marked area of (B).



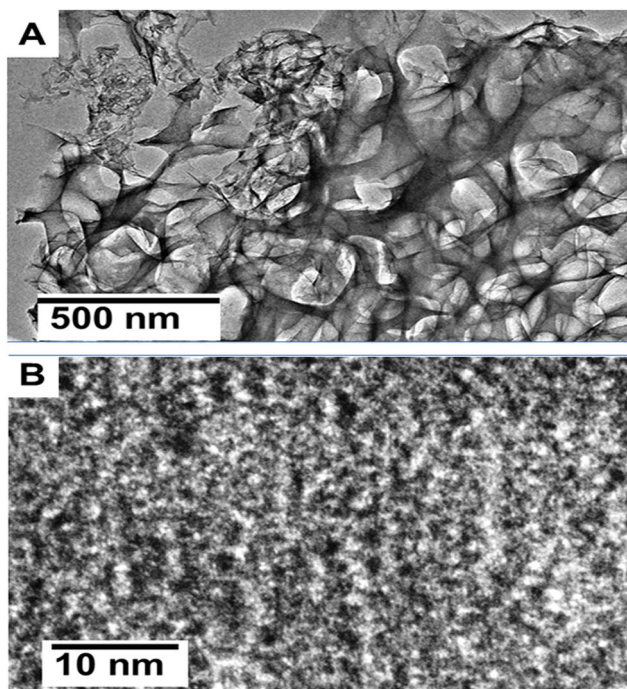


Fig. 2 (A) TEM and (B) HRTEM images of carbon nanosheets prepared from tal palm leaves at 850 °C.

broad peak indicates the presence of a small amount of graphitic carbon.

X-ray photoelectron spectroscopy (XPS) analysis was performed to examine the elemental composition of the prepared porous carbon nanosheets, which were heat-treated at 850 °C. All the XPS spectra were corrected with respect to the standard C1s peak at 284.6 eV. As shown in Fig. 4(A), the XPS survey spectrum of the porous carbon nanosheets consists of three different peaks located at 284.6, 488.6 and 531.6 eV, which can be assigned to C1s, Sn3d and O1s, respectively. Here, the peaks for C and O are expected to be from the carbon nanosheets. The reason for the additional Sn peak is due to the substrate FTO-coated glass as the carbon nanosheets were immobilized on that for recording the XPS spectra. The XPS spectrum of C1s [Fig. 4(B)] was deconvoluted into three peaks at 284.6 eV labelled as C-I, which is linked with the sp² hybridized C-C

bond.²⁴ The additional peaks at 285.3 labelled as C-II and 286.7 labelled as C-III eV could be assigned to sp³ carbon (C-C bond) and C=O/C-O bonds, respectively.²⁷ Fig. 4(C) shows the O1s spectrum at 531.3 eV, related to numerous oxygen functionalities. The deconvolution of O1s peak resulted in four peaks at different binding energies. The one labelled as O-I and centred at 531.3 eV represents carbonyl oxygen (O=C), the second peak labelled as O-II and centred at 532.4 eV can be attributed to carbonyl oxygen in carboxylic as well as oxygen atoms in hydroxyl groups (COOH), the overlapping O-I and O-II peaks represent Sn-O bonding, while the third peak labelled as O-III and centred at 533.2 eV represents the C-O.^{28–31} The peak at 536.1 eV labelled as O-IV shows evidence for the presence of nitrogen by the N-C=O bonding.³² The presence of N was very trace as we failed to detect a N peak in the survey spectrum as well as failed to get a well-defined characteristic N1s spectrum.

The nitrogen adsorption-desorption isotherms for the synthesized porous carbon nanosheets at 850 °C are shown in Fig. 5(A). This result indicated a type-II adsorption-desorption isotherm of the porous carbon nanosheets with a high nitrogen adsorption-desorption capacity.²⁴ Due to the formation of mesopores, the sample showed a wider hysteresis loop from $P/P_0 = 0.01$ to $P/P_0 = 1$. The specific Brunauer-Emmett-Teller (BET) surface area of the porous carbon nanosheets was 1094.53 m² g⁻¹ and 0.74 cm³ g⁻¹ respectively. The corresponding Barrett-Joyner-Halenda (BJH) pore-size distribution of porous carbon nanosheets is shown in Fig. 5(B). This result represents a wide distribution of pore width (range: 2 to 180 nm) with an average pore size of 22 nm, which shows the existence of macro- and mesopores.²⁹ The coexisting of macro- and mesopores not only increases the specific surface area but also offers high availability for ions.³⁰ Mostly, materials with a hierarchical porous structure and large specific surface area play a vital role for the improvement of electrochemical properties. Therefore, the porous carbon nanosheets were considered to have high-performance electrode properties for electrochemical sensors applications.

A comparable study was made to inspect closely the electron-transfer capacity of the prepared PTPCNs/GCE sensor at the interface region by CV and electrochemical impedance spectroscopy (EIS) analysis, where standard 5 mM ferricyanide in 1.0 M support KCl was chosen as the electroactive species.

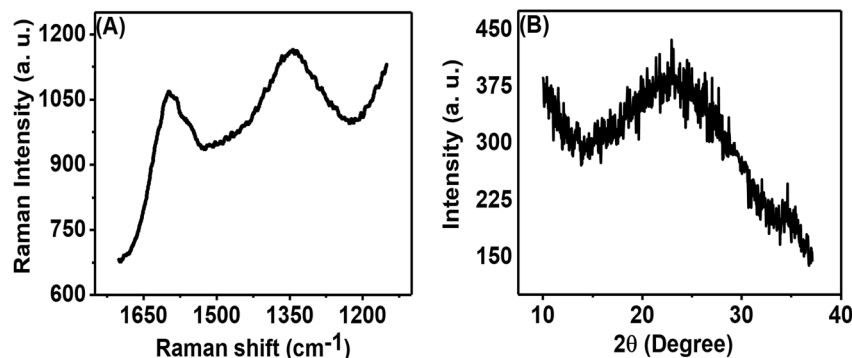


Fig. 3 (A) Raman and (B) XRD spectra of carbon nanosheets prepared from tal palm leaves.



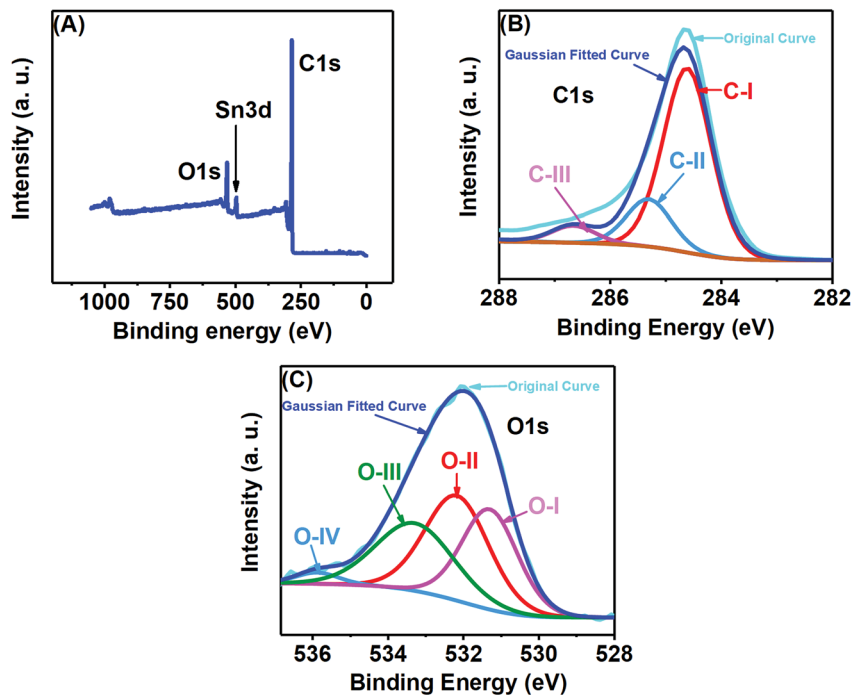


Fig. 4 (A) XPS survey spectrum, (B) C1s and (C) O1s deconvoluted XPS spectra of the porous carbon nanosheets prepared from tal palm leaves.

Fig. 6(A) shows the corresponding CVs of bare GCE (a) and the PTPCNs/GCE (b) for the electrochemical redox reaction of the active ferricyanides. A notable increase in both redox peak currents was observed in the proposed sensor. The enhancement of the cathodic to anodic peak currents was quite similar, confirming the facile electrochemical redox reactions and reversibility of the peak responses. Meanwhile, the peak-to-peak separation was small enough to be in good agreement with the theoretical value, which affirmed the diffusion controlled redox change at the proposed PTPCNs/GCE. This observation confirmed that the PTPCNs-modified GCE surface could effectively facilitate electron transfer with the ferricyanides. In contrast, the bare GCE although exhibited a reversible pair but

the response was less significant compared to the modified GCE.

In Fig. 6(B), Nyquist plots of the respective bare electrode (a) and PTPCNs/GCE (b) are shown for the same 5 mM ferricyanide solution. The semicircle portion at the high-frequency region expresses the charge-transfer resistance (R_{ct}), while the straight portion expresses the diffusion-controlled mass transfer related to the Warburg resistance (W), for the faradaic process. The larger value of the slope of the straight line refers to a low W . Here, a significant change in the semicircle shape was observed for the modified sensor in comparison to the conventional GCE. A lower value of R_{ct} at PTPCNs/GCE indicated a low R_{ct} or a fast electron transfer rate at the interface. This observation further evinced the presence of negative charges at PTPCNs as stated above. The presence of the graphitic structure in the carbon nanosheets could probably be the reason, offering the existence of a large number of free charges on the surface, which would facilitate electron transfer from PTPCNs to the redox probe. Besides, the presence of C–O or C=O, –OH, –COOH groups in the carbon nanosheets facilitated the electron-transfer reactions also.

3.2. Electrochemical behaviour of DA and UA at the PTPCNs/GCE

The CV and differential pulse voltammetry (DPV) responses of DA and UA are represented in Fig. 5 and assist us in understanding the electrochemical redox behaviours of these corresponding analytes at the modified PTPCNs/GCE. In all these experiments [Figs 7(A)–(F)], the bare GCE responses were accounted for too in order to make a quick comparison with the modified PTPCNs/GCE responses obtained for DA and UA.

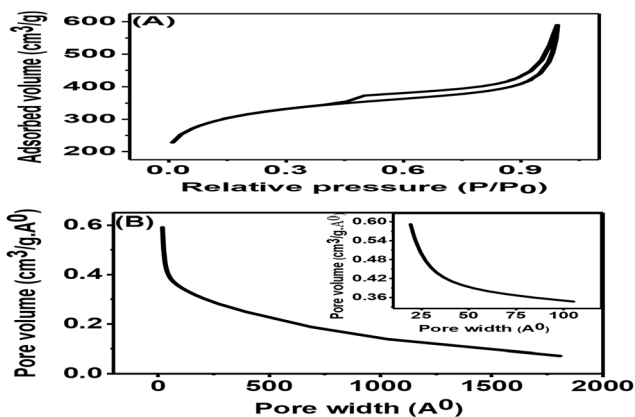


Fig. 5 (A) Nitrogen adsorption–desorption isotherm and (B) corresponding BJH pore-size distributions of porous carbon nanosheets prepared from tal palm leaves at 850 °C. Inset of (B) is the corresponding low pore width zone.



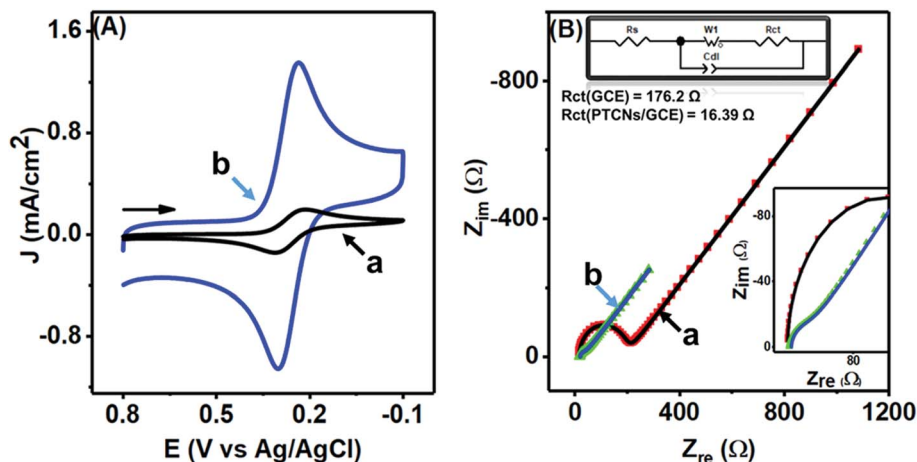


Fig. 6 (A) CVs and (B) EIS spectra of 5.0 mM $K_3[Fe(CN)_6]$ in 1.0 M KCl at the GCE (a) and at the PTPCNs/GCE (b). The upper left side of (B) shows the Randles circuit, whereas the lower left inset shows the magnified EIS of the PTPCNs/GCE.

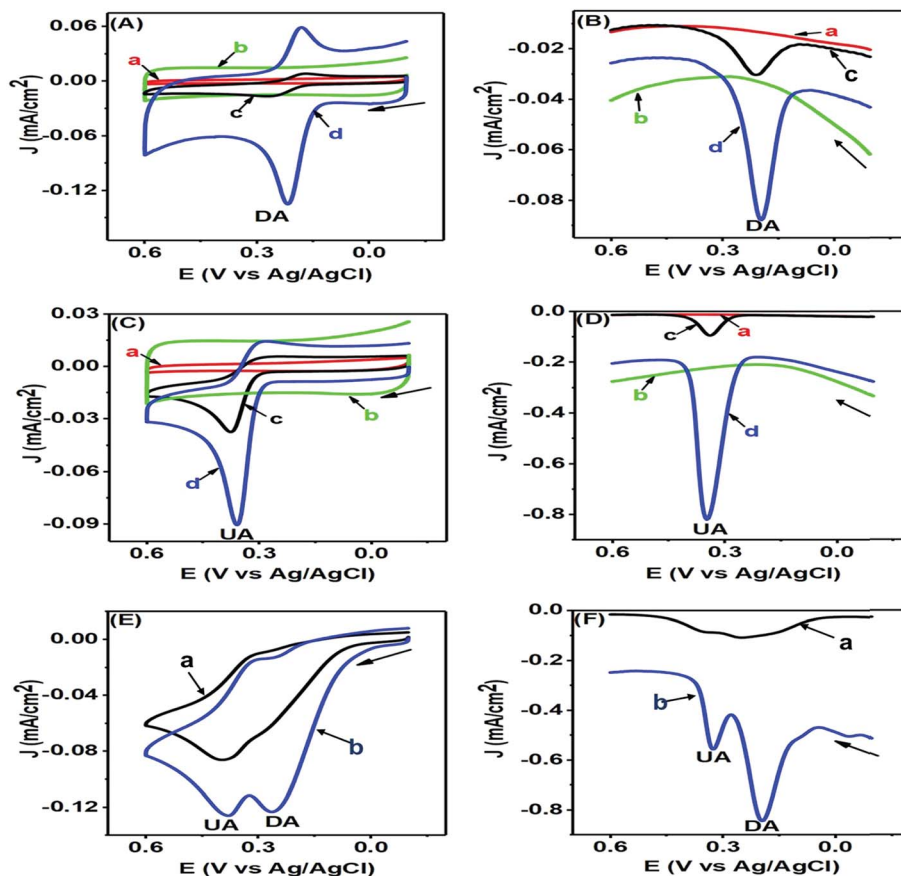


Fig. 7 CVs (A) and DPVs (B) of blank 0.1 M PBS solution of pH 7.0 (a and b) and 50 μ M DA (c and d) in the same PBS of pH 7.0 at the GCE (a and c) and PTPCNs/GCE (b and d). CVs (C) and DPVs (D) of blank 0.1 M PBS of pH 7 (a and b) and 200 μ M UA (c and d) in PBS of pH 7.0 at the GCE (a and c) and PTPCNs/GCE (b and d). CVs (E) and DPVs (F) of the mixture of 50 μ M DA and 200 μ M UA in 0.1 M PBS of pH 7.0 at the bare GCE (a) and PTPCNs/GCE (b).

Fig. 7(A) shows the CVs of 50 μ M DA in 0.1 M PBS of pH 7.0 at the GCE (c) and PTPCNs/GCE (d) and the corresponding CVs of blank PBS solution at the GCE (a) and PTPCNs/GCE (b). The CV of DA obtained at the PTPCNs/GCE exhibited two redox peaks with about 5 and 2 times enlargement of the corresponding

oxidation and reduction peaks compared to those obtained at the bare GCE. This confirmed the successful electro-oxidation of DA to dopamine-*o*-quinone (DAQ) with successive reduction later in the reverse scan. However, the reduction peak was not amplified enough like the oxidation peak due to the low stability



of the oxidized form DAQ, which underwent chemical cyclization.¹⁰ The peak separation (ΔE_p -65 mV) was quite consistent with the theoretical value, reflecting a reversible redox reaction of DA at the PTPCNS/GCE. In Fig. 7(B), DPVs of $50 \mu\text{M}$ DA at the bare GCE (c) and PTPCNS/GCE (d) were obtained, displaying quite analogous responses as observed in the CV analysis. The oxidation peak observed in 0.19 V at PTPCNS/GCE was 5 times more enhanced compared to that of the bare GCE.

The CVs of $100 \mu\text{M}$ UA at the bare GCE (c) and PTPCNS/GCE (d) in a similar 0.1 M buffer of pH 7.0 and the CVs of blank PBS solution at the bare GCE (a) and PTPCNS/GCE (b) are shown in Fig. 7(C). The CV of UA at the PTPCNS/GCE exhibited a sharp response at 0.35 V, confirming its fast oxidation to the quinoid diimine form at the modified electrode surface.³³ However, no clear reduction peak was observed at the PTPCNS/GCE, as the oxidized quinoid diimine form was no longer capable of reducing back at the same rate. The DPV, on the other hand, in Fig. 7(D), of the same $100 \mu\text{M}$ UA showed a sharp peak for the oxidation of UA at the modified PTPCNS/GCE (d), which was about 5 times greater than that of the bare GCE (c), as expected.

Simultaneous changes in the electrochemical responses of both DA and UA at the PTPCNS/GCE were again studied by means of CV and DPV, as shown in Fig. 7(E) and (F). Both figures display the corresponding CV and DPV responses of the mixture of $50 \mu\text{M}$ DA and $200 \mu\text{M}$ UA in 0.1 M PBS solution at the bare GCE (a) and PTPCNS/GCE (b). Here in both CV and DPV, PTPCNS/GCE had successfully resolved the electro-oxidation peaks of both DA and UA at 0.21 and 0.35 V, respectively. The peak responses of DA in both CV and DPV were relatively more intense than that of UA at the PTPCNS/GCE, depicting a faster and more pronounced electron-transfer capacity between the

electrode surface and DA. In contrast, the bare GCE failed to give well-resolved peak responses for the concurrent detection of DA and UA in both CV and DPV. These findings confirmed the suitability of the PTPCNS-modified GCE electrode for their (DA and UA) simultaneous detection.

3.3. Effect of the scan rate

CV is of particular interest for studying the kinetics of an electrochemical reaction through the scan rate variation. Fig. 8(A) shows the electrochemical changes associated with the scan rate variation (50 – 500 mV s^{-1}) in a mixture of $50 \mu\text{M}$ DA and $200 \mu\text{M}$ UA. The peak currents of both analytes increased with increasing scan rates, while the potential remained unaltered, further confirming that both analytes underwent reversible electrochemical changes. We can use the information obtained from the scan rate variation to determine whether an electrochemical process is diffusion (J_p vs. $\nu^{1/2}$) or adsorption (J_p vs. ν) controlled. The plots in Fig. 8(B) and (C) for DA and UA showed that both oxidation and reduction currents for DA and UA were linear from 50 – 500 mV s^{-1} . The correlation coefficients for UA and DA were found to be 0.99559 and 0.99656 for oxidation and 0.99271 and 0.9973 for reduction peak currents, respectively, indicating that the electrochemical redox process was diffusion controlled for both analytes at the PTPCNS/GCE.³⁴

3.4. Effect of pH

The pH of a solution is a measure of the proton (H^+) strength of the solution. The analytes present in a solution are modified according to their protonated (in acidic medium) or deprotonated (in basic medium) forms with the change in pH of

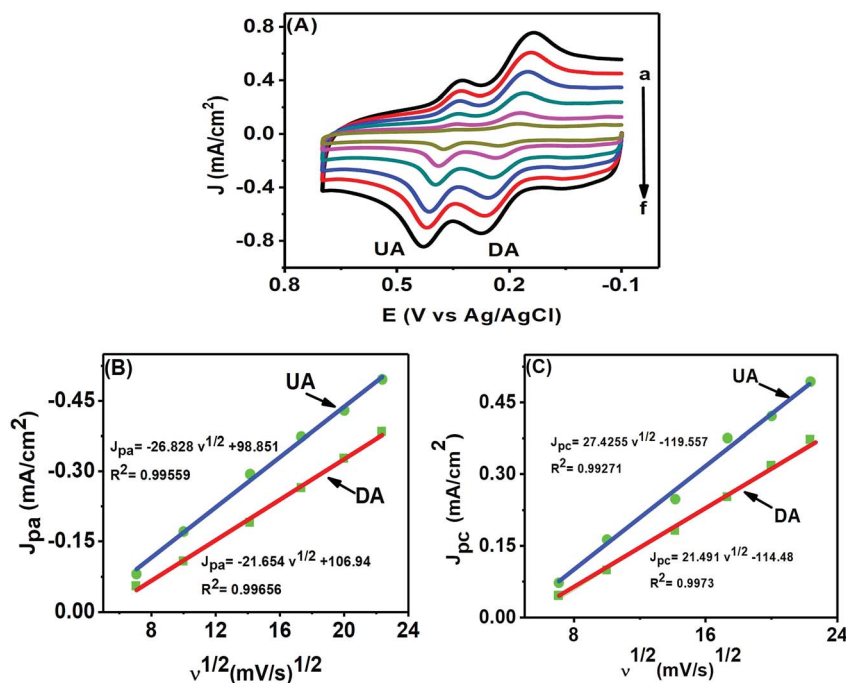


Fig. 8 (A) CVs of $50 \mu\text{M}$ DA and $200 \mu\text{M}$ UA at the PTPCNS/GCE in 0.1 M PBS of pH 7.0 at different scan rates (a–f): 50 , 100 , 200 , 300 , 400 , 500 mV s^{-1} . The relationship between the oxidation peak current densities (B) and reduction peak current densities (C) of DA and UA with the square root of the scan rates.



μM in the potential window of 0.0–0.1 V. We plotted the peak currents of DA and UA observed for varying concentrations of AA in Fig. 10(B). The presence of high concentrations of AA (till measured to 1 mM of AA) had only a slight effect on the charging current and on the peak current of the analytes. As the concentration of AA was increased from 100 μM to 1 mM, the DA and UA peak currents varied slightly (R.S.D. = 3.53% for DA and 3.03% for UA) and the peaks could be clearly identified. However, when 1.5 mM AA was in solution, the peak current changed drastically (R.S.D. = 9.34% for DA and 3.10% for UA), while the DA peak current increased, the UA peak started decreasing, making it difficult to separate the individual peaks. Since, the sensor was able to detect DA and UA simultaneously with limited interference from AA up to 1 mM, hence, the PTPCNS/GCE sensor could be suitable for the *in vivo* simultaneous detection of the analytes in the presence of AA.


3.6. Theoretical discussion on possible interaction between the PTPCNS/GCE and analytes

From experimental observations, it was obvious that both DA and UA underwent simultaneous redox reaction at the PTPCNS/GCE. The diffusivity of DA and UA in that case was greatly influenced by the morphology and conductivity of the PTPCNS obtained from tal palm leaves. The specific surface area, nature of the porosity, pore size, nano framework and surface functionalities were the important parameters that could explain the

high conductivity of such activated tal carbon nanosheets and their response to DA and UA. Here the possible explanation of how the electroactive species, DA and UA, interact with the proposed sensor are briefly discussed.

A defect and chemical composition study by Raman and XPS of the porous carbon nanosheets confirmed the presence of a significant number of sp^2 hybridized carbons (*i.e.* graphitized structure). This could possibly result from the high-temperature carbonization of the NaHCO_3 -treated carbon mass.³⁶ The graphitic domain of PTPCNS possessed a comparable amount of free electrons, which induced a great number of non-covalent type interactions, namely π - π , with electroactive species DA and UA.¹⁰ In addition, the specific nano level thickness of the PTPCNS could have provided an effective and suitable interface between the electrode and solution that minimized the pathway for mass and electron transfer, thus increasing the rate of electron transfer for DA and UA.³⁷

BET isotherm and pore size distribution curves affirmed the firmly distributed porous framework of the carbon nanosheets, consisting of an interconnected network of meso and macro pores. During the pyrolysis, the pulverized mass released O and H elements as H_2O , CO and CO_2 for producing porous carbon nanosheets.^{36,38} The FESEM image in Fig. 1(C) as well as the wider hysteresis loop observed in the BET isotherm in Fig. 5(A) revealed that the porous frame was developed appreciably in an ordered hierarchical form that enhanced the diffusivity of DA

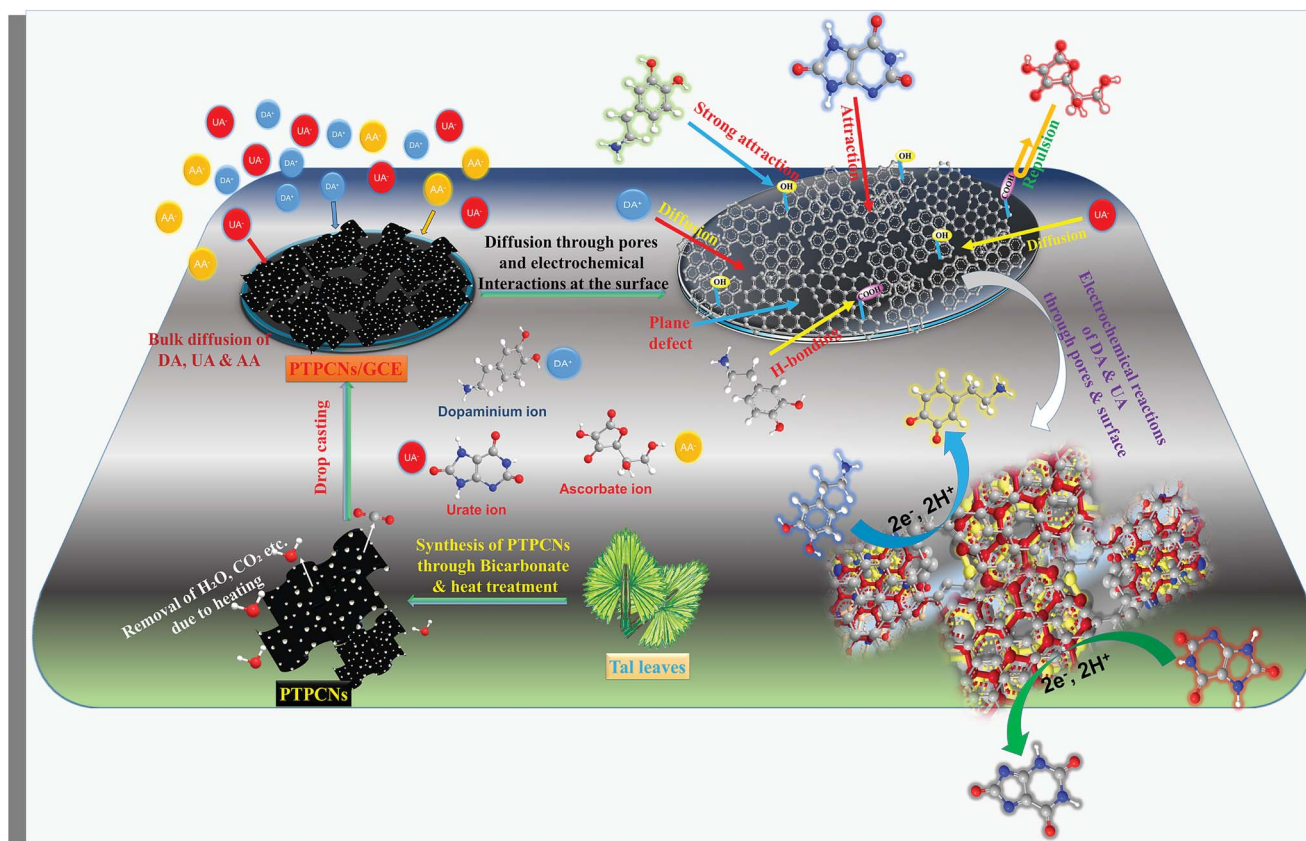

Scheme 3 Simple portrayal of the formation of pores in the PTPCNS, bulk diffusion of DA^+ , UA^- and AA^- at the PTPCNS/GCE, their interactions with the PTPCNS/GCE and electrochemical reactions of DA and UA through the surficial pores as well as the surface.



and UA at the PTPCNs/GCE by reducing the tortuosity.³⁹ The mass transport capacity often becomes difficult through ultra as well as micro porous frameworks due to its short diameter, which eventually declines the accessibility of electrolytic species to the sensor. Here, the hierarchical macro and meso porous structure of the PTPCNs were most likely allowed a marked diffusion of electroactive species by making use of the internal porous network.³⁸ Hence, the resultant large specific surface area facilitated the electrochemical reactions of DA and UA at the PTPCNs/GCE. Such porous carbon formed from tal palm leaves also exhibited high capacitive currents when being drop-casted as more than 5 μL on the GCE. This capacitive current lowered the oxidation peak current height for both DA and UA due to enlargement of the double layer thickness. This is why 5 μL of PTPCNs was chosen as the optimized amount for electrode modification.

Surface functionalities are very important because they offer preferable interactions at the interface between analytes and functional groups. EDS study confirmed the presence of surficial elemental O atoms, while XPS analysis proved the existence of $-\text{C}-\text{O}$, $-\text{C}=\text{O}$, $-\text{COOH}$ and $-\text{OH}$ functional groups on the PTPCNs. The high-temperature carbonization at 850 $^{\circ}\text{C}$, however, considerably reduced the oxygenated groups by means of releasing H_2O , CO and CO_2 , but some of the groups could still be saved at this temperature level.³⁶ These functional groups

were mostly hydrophilic in nature and thus provided a suitable surface for interacting with analytes.³⁷ The comparatively higher sensitivity of DA towards the PTPCNs/GCE than UA could possibly be due to the more preferable formation of short-range hydrogen bonding by utilizing its two $-\text{OH}$ and one $-\text{NH}_2$ group.¹⁰

The pH variation study of both DA and UA from pH 5–9 further validated the existence of negative functionalities on the PTPCNs. At pH 7, UA and AA preferentially bear negative charge and are converted to urate and ascorbate ions, while DA in a medium of pH 7 mostly exists in cationic form.¹⁰ Hence, the surface reactivity of DA was greater due to the existence of attractive forces between the negative functionalities of porous carbon and positively charged DA. Meanwhile, the repulsive force that acted for both urate and ascorbate ions at the PTPCNs/GCE were not similar. Charge density on ascorbate ions is relatively higher than on urate ions. Hence, enhanced repulsive interactions at the surface reduced the diffusion and then oxidation of AA drastically at the proposed sensor. This might have been the reason why the PTPCNs/GCE showed only a very poor response towards AA even at high concentrations, as was observed during the interference studies. We show the possible interactions between the PTPCNs and analytes through graphical representation in Scheme 3.



Fig. 11 DPVs of various concentrations of (A) DA with fixed concentration of UA (100 μM) and (C) UA with fixed concentration of DA (10 μM) in 0.1 M PBS at pH 7.0 at the PTPCNs/GCE. (A) Concentrations of DA (a–l) are: 1, 3, 5, 10, 20, 25, 30, 40, 50, 60, 75, 100 μM and for (C) concentrations of UA (a–p) are: 5, 7, 10, 15, 20, 25, 30, 40, 50, 60, 75, 100, 125, 150, 175, 200 μM . The corresponding calibration plots (J_p vs. concentration) of DA and UA are shown in (B) and (D).



- 31 M. Genovese, J. Jiang, K. Lian and N. Holm, *J. Mater. Chem. A*, 2015, **3**, 2903–2913.
- 32 N. Karikalan, M. Velmurugan, S.-M. Chen, C. Karuppiah, K. M. Al-Anazi, M. A. Ali and B.-S. Lou, *RSC Adv.*, 2016, **6**, 71507–71516.
- 33 G. Fabregat, J. Casanovas, E. Redondo, E. Armelin and C. Alemán, *Phys. Chem. Chem. Phys.*, 2014, **16**, 7850–7861.
- 34 L. Yang, D. Liu, J. Huang and T. You, *Sens. Actuators, B*, 2014, **193**, 166–172.
- 35 A. J. S. Ahammad, X. Li, M. Rahman, K. Noh and J. Lee, *Int. J. Electrochem. Sci.*, 2013, **8**, 7806–7815.
- 36 C. Wang, Q. Lai, K. Feng, P. Xu, X. Li and H. Zhang, *Nano Energy*, 2018, **44**, 240–247.
- 37 C. Matei Ghimbeu, J. Górká, V. Simone, L. Simonin, S. Martinet and C. Vix-Guterl, *Nano Energy*, 2018, **44**, 240–247.
- 38 S. Y. Lu, M. Jin, Y. Zhang, Y. B. Niu, J. C. Gao and C. M. Li, *Adv. Energy Mater.*, 2018, **8**, 1–9.
- 39 A. B. Deshmukh, A. C. Nalawade, I. Karbhal, M. S. Qureshi and M. V. Shelke, *Carbon*, 2018, **128**, 287–295.
- 40 D. A. Armbruster and T. Pry, *Clin. Biochem. Rev.*, 2008, **29**, S49–S52.
- 41 H. Bagheri, N. Pajoohehpour, B. Jamali, S. Amidi, A. Hajian and H. Khoshafar, *Microchem. J.*, 2017, **131**, 120–129.
- 42 D. Zhang, L. Li, W. Ma, X. Chen and Y. Zhang, *Mater. Sci. Eng., C*, 2017, **70**, 241–249.
- 43 J. Wang, B. Yang, J. Zhong, B. Yan, K. Zhang, C. Zhai, Y. Shiraishi, Y. Du and P. Yang, *J. Colloid Interface Sci.*, 2017, **497**, 172–180.
- 44 L. Fu, A. Wang, G. Lai, W. Su, F. Malherbe, J. Yu, C. Te Lin and A. Yu, *Talanta*, 2018, **180**, 248–253.

