

Cite this: *Nanoscale Adv.*, 2024, 6,
1286

Recent developments, advances and strategies in heterogeneous photocatalysts for water splitting

Muhammad Sohail,^a Sana Rauf,^b Muhammad Irfan,^c Asif Hayat,^d Majed M. Alghamdi,^e Adel A. El-Zahhar,^e Djamel Ghernaout,^{fg} Yas Al-Hadeethi,^{hij} and Weiqiang Lv^{*a}

Photocatalytic water splitting (PWS) is an up-and-coming technology for generating sustainable fuel using light energy. Significant progress has been made in the developing of PWS innovations over recent years. In addition to various water-splitting (WS) systems, the focus has primarily been on one- and two-steps-excitation WS systems. These systems utilize singular or composite photocatalysts for WS, which is a simple, feasible, and cost-effective method for efficiently converting prevalent green energy into sustainable H₂ energy on a large commercial scale. The proposed principle of charge confinement and transformation should be implemented dynamically by conjugating and stimulating the photocatalytic process while ensuring no unintentional connection at the interface. This study focuses on overall water splitting (OWS) using one/two-steps excitation and various techniques. It also discusses the current advancements in the development of new light-absorbing materials and provides perspectives and approaches for isolating photoinduced charges. This article explores multiple aspects of advancement, encompassing both chemical and physical changes, environmental factors, different photocatalyst types, and distinct parameters affecting PWS. Significant factors for achieving an efficient photocatalytic process under detrimental conditions, (e.g., strong light absorption, and synthesis of structures with a nanometer scale. Future research will focus on developing novel materials, investigating potential synthesis techniques, and improving existing high-energy raw materials. The endeavors aim is to enhance the efficiency of energy conversion, the absorption of radiation, and the coherence of physiochemical processes.

Received 22nd June 2023
Accepted 28th December 2023

DOI: 10.1039/d3na00442b

rsc.li/nanoscale-advances

1. Introduction

The global growth of urban regions, along with increasingly demanding environmental rules, has led to a substantial surge in global fuel consumption and an increasing of ecological

degradation.^{1–5} Renewable energies are pivotal in revitalizing the transportation and economic sectors, comprising nearly 90% of renewable energy and contributing to decreasing of greenhouse gas and aerosol emissions, including carbon dioxide (CO₂). As a result, there is a significant decrease in the use of carbon-containing materials for constructing positive additions.^{6–8} In 2013, global fuel expenditure reached 17 TW. It is expected to almost get thrice by 2050.⁹ Developing a clean and sustainable fuel source is crucial for reducing the impacts of carbon emissions, such as global warming, and addressing issues such as depletion of fuel inventory levels, asset specificity, and dependence on sizeable global fuel suppliers.^{10–13} There are numerous substitutes for traditional fuel resources, such as wind, solar thermal, hydroelectric, and photovoltaic, which are cleaner and more sustainable than traditional energy sources. However, every alternative has limitations that make the move away from traditional fuels harder to accomplish. For example, wind power resources cannot store the energy they generate.¹⁴ The reconstruction limitations impede geothermal power development owing to high costs and probable environmental implications. Similarly, while solar electricity is a renewable source, it has a limited lifetime and hence incurs significant operating costs.¹⁵ Nonetheless, solar radiation is unlimited, sustainable, independent, and capable of producing electric energy or temperature

^aHuzhou Key Laboratory of Smart and Clean Energy, Yangtze Delta Region Institute (Huzhou), University of Electronic Science and Technology of China, Huzhou 313001, P. R. China. E-mail: eselwq@uestc.edu.cn

^bCollege of Physics and Optoelectronic Engineering, Shenzhen University, Shenzhen 518060, PR China

^cDepartment of Chemistry, Hazara University, Mansehra 21300, Pakistan

^dCollege of Chemistry and Life Sciences, Zhejiang Normal University, 321004 Jinhua, Zhejiang, P. R. China

^eDepartment of Chemistry, College of Science, King Khalid University, P. O. Box 9004, Abha, 61413, Saudi Arabia

^fChemical Engineering Department, College of Engineering, University of Ha'il, PO Box 2440, Ha'il 81441, Saudi Arabia

^gChemical Engineering Department, Faculty of Engineering, University of Blida, PO Box 270, Blida 09000, Algeria

^hPhysics Department, Faculty of Science, King Abdulaziz University, Jeddah 21589, Saudi Arabia

ⁱLithography in Devices Fabrication and Development Research Group, Deanship of Scientific Research, King Abdulaziz University, Jeddah 21589, Saudi Arabia

^jKing Fahd Medical Research Center (KFMRC), King Abdulaziz University, Jeddah 21589, Saudi Arabia



without requiring expensive turbine blades or installation. On one hand, solar radiation on planet's surface may generate enough fuel to power it for a continuous year.^{16–18} On the other hand, the quantity of energy produced by natural light is limited by geological location, time of day, duration, and weather conditions.^{19,20} Another drawback of renewable radiation is the variation in light intensity across the different regions of Earth.²¹ Developing a recyclable, clean, consistent, and sustainable fuel is imperative to meet the global demand. The primary objective of renewable energy exploration is to generate an artificial photosynthesis system capable of effectively converting sunlight into chemical fuel.²² Plants carry out the procedure of transforming energy through natural photosynthesis, whereby CO₂ and water are alternately transformed into oxygen and carbohydrates by using visible light. Utilizing synthetic photocatalysts to imitate this procedure and separate water into hydrogen (H₂) and oxygen (O₂) is an attractive method for generating environmentally friendly and sustainable H₂ fuel.^{23–25} Considering its remarkable nature, the existing photocatalytic systems and compounds are not yet suitable for real-world deployment owing to their poor solar-to-hydrogen (STH) conversion rate, which is generally under 1%.²⁶ To achieve this objective, it is crucial to use an organized strategy to develop and produce water-splitting (WS) photocatalysts that exhibit exceptional efficiency. These photocatalysts should be capable of exploiting sunlight to break down purified water into equal quantities of H₂ and O₂, with no need for any

other reagents. The exploration of this WS system has continued since 1980.^{24,27,28} Since then, several materials with the ability to produce H₂ and O₂ from pure water have been discovered. Nevertheless, the majority of the materials consist of inorganic semiconductors, which possess optical and electrical characteristics that can only be adjusted within a specific range of values. Throughout this work, we describe photocatalytic overall water splitting (POWS), including theoretical modeling, reaction conditions, core design ideas, current breakthroughs in different photocatalyst synthesis, multiple parameters for enhancing POWS, and potential future outlook for such a unique process as summarized in Fig. 1.

1.1. Fundamentals of photocatalytic overall water splitting (POWS)

OWS refers to a thermodynamically unfavorable process ($\Delta G > 0$), requiring external energy input to facilitate the decomposition of H₂O into H₂ and 1/2O₂.^{29–35} In heterogeneous photocatalysis, the utilization of light serves as the external energy source, providing the necessary energy input to facilitate OWS. The photocatalytic process initiates when photons are absorbed, and their wavelengths either match or exceed the energy level of the band gap. The energy state of the photocatalyst needs to align with the thermodynamics of WS (into H₂ and O₂) to facilitate the efficient execution of the process. The pH level

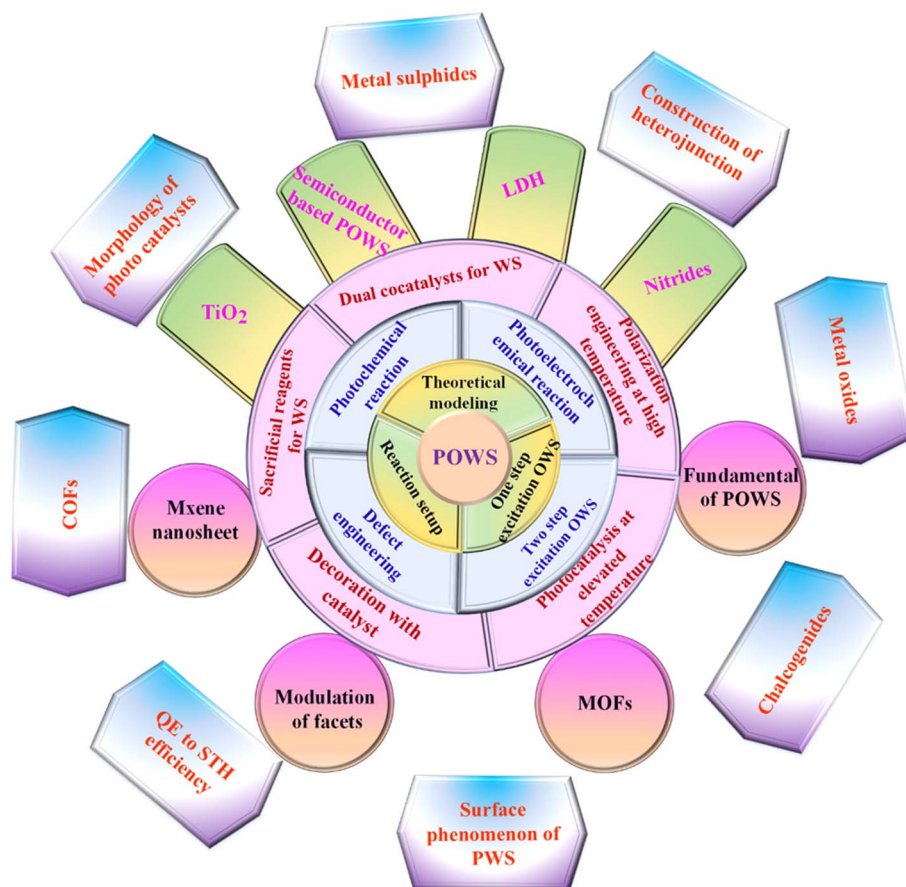


Fig. 1 The overview of all aspects of this review.



of water plays a crucial role in influencing these reactions. The semiconductor must possess a minimum band gap of 1.23 V under standard conditions to meet the thermodynamic criteria. Specifically, the potentials of the valence band (VB) and conduction band (CB) should be 1.23 V and 0 V, respectively. Beyond thermodynamic considerations, an additional overpotential is necessary to surmount the activation energy barrier associated with the hydrogen evolution reaction (HER) and the oxygen evolution reaction (OER). This overpotential enables the production of H_2 and O_2 at a measurable rate.³⁶ The effectiveness of the photocatalytic process in converting light energy into the chemical energy of the resulting products is influenced by a multitude of factors.^{37–44} The initial separation of charges induced by the light occurs within a very short time frame (\sim femtoseconds), leading to the separation of charges.^{45,46} However, this is followed by undesired electron–hole recombination, which can occur within the picosecond to millisecond

time range. This recombination can happen either at the site where charge separation occurred (known as “geminate recombination”) or after charge carriers have migrated and randomly encountered each other. The efficiency of the overall process is greatly influenced by the occurrence of charge recombination through any of these pathways.^{45–48} Several factors constrain the efficiency of a photocatalyst. One such limiting factor is the occurrence of the OWS back reaction, which leads to the generation of H_2O from the produced H_2 and O_2 . This reaction is thermodynamically favored with a $\Delta G = -237 \text{ kJ mol}^{-1}$.^{37,38} The significance of this reverse reaction increases when co-catalysts, such as platinum (Pt) nanoparticles, are introduced (Fig. 2a and b).^{26,49} These nanoparticles are recognized for their ability to enhance traditional catalytic or photocatalytic H_2 reactions involving O_2 .⁵⁰ In terms of photocatalysis, it is possible for electrons and holes to undesirably react with O_2 or H_2 , resulting in the formation of $O_2 \cdot^-$ and H^+ ,

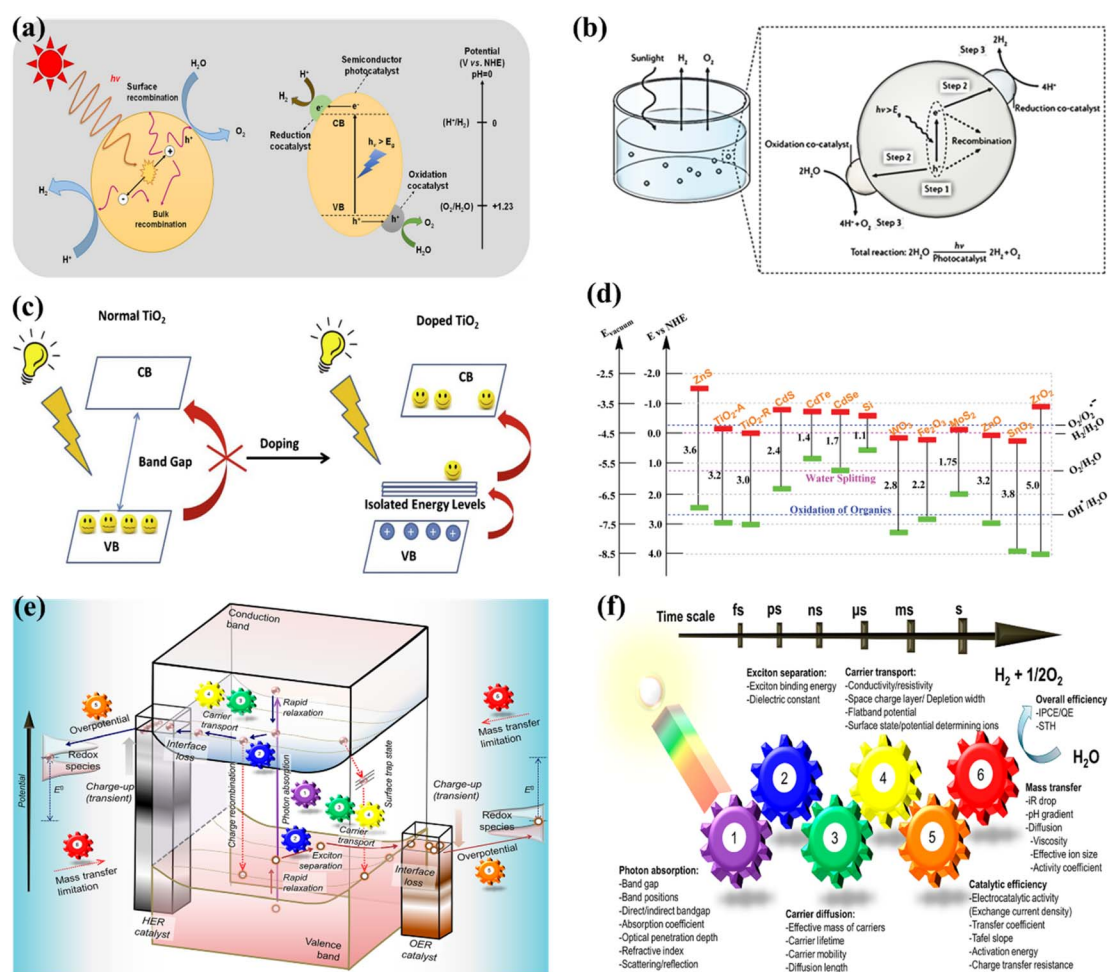


Fig. 2 (a) Schematic representation of POWS. Adapted from ref. 49. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license, (b) diagram depicting the fundamental steps involved in the POWS process. Adapted from ref. 26. Copyright © 2017, Springer Nature, (c) illustration of the process by which the band gap of TiO_2 is reduced with the inclusion of anions. Adapted from ref. 60. Copyright © 2015, Elsevier, (d) the band gap energy, and the VB and CB for various semiconductors via NHE. Adapted from ref. 62. Copyright © 2015, Royal Society of Chemistry, (e) illustration depicting the procedure of PWS. A gear corresponding to the numerical value signifies the sequential arrangement of the photocatalytic reaction required for the effective achievement of OWS, (f) photocatalysis factors. OWS is efficient when all six gears represented in the design operate with significant efficiency. This is an open access publication licensed under CC-BY-NC-ND.⁶⁵



respectively. Even though it has not been extensively researched, the overall efficiency of photocatalysis can also be influenced by mass transfer limitations.⁵¹ In the case of porous solids, diffusion plays a significant role as it can affect gas evolution due to factors such as pore size, adsorption capacity, hydrophilicity, speed of stirring, or reactor.

1.2. Semiconductor based photocatalytic water splitting

Both half reactions of WS were thoroughly studied to examine the correlation between the photocatalyst structure and their properties and achieve the desired WS performance. In the H₂ and O₂ evolution process, a sacrificial reagent is commonly adopted to enhance yielding. Adding a sacrificial agent to a catalyst may catalyze both reactions, but it may not be sufficient for OWS. A photocatalyst with a 2 : 1 ratio is employed to directly produce H₂ and O₂ from water. Numerous research and review articles have proposed mechanisms for the photo-assisted PWS process.^{52–58} The process begins with photon absorption, which produces electron-hole pairs, that have a high probability of initiating the reaction. Subsequently, the photo-generated hole pairs migrate to the catalyst surface to interact with active sites.⁵⁹ Ultimately, photogenerated electrons are responsible for converting water molecules into H₂, while holes are responsible for oxidizing water molecules to form O₂^{•-}. Similarly, Fujishima and Honda were the first to show the PWS capabilities of a TiO₂ electrode in their landmark research.²⁹ Since then, research into WS using semiconductor materials has predominantly focused on heterogeneous catalysis. More importantly, various WS research studies on semiconductor materials have been conducted primarily using heterogeneous catalysis. Semiconductors have a non-overlapping CB and VB, and the photochemical energy accelerates electrons into the CB, resulting in electron holes in the VB and a surplus of electrons in the CB (Fig. 2c).⁶⁰ These electron-hole pairs are crucial in the redox reactions that occur during WS. Electrons convert protons into H₂, while anions oxidize holes (O²⁻). For the redox reaction to begin (normal hydrogen electrode, NHE), the VB must be higher than the water oxidation level (EO₂ vs. H₂O, 1.23 eV vs. 1.23 eV). To achieve a bandgap of 1.23 eV, WS catalysts are preferred. The possible materials for PWS include KTaO₃, ZrO₂, SrTiO₃, BiVO₄, TiO₂, and BiVO₄, owing to their diverse photocatalytic properties.⁶¹ However, photo-corrosion causes conventional semiconductors such as SiC, ZnO, and CdS to lose their capacity to operate as WS catalysts (Fig. 2d).⁶² Photo-corrosion occurs when photogenerated holes oxidize the anion in the catalyst. Moreover, most semiconductor catalysts operate only under ultraviolet (UV) light, which accounts for only 4% of total solar energy, limiting their efficiency. Similarly, visible light photocatalysts are highly beneficial to enhance solar energy efficiency, as visible light accounts for almost half of all solar energy, and semiconductor materials with bandgaps less than 3 eV can respond to visible light. The addition of carbon or precious metal particles to semiconductor catalysts can improve their visible light response. Furthermore, photocatalysts that employ metal sulfides or nitrides can split water under visible light, as reported in studies.^{63,64} Fig. 2e illustrates the utilization

of a singular semiconductor particle as a photocatalyst, adorned with HER and OER catalysts on its surface, having the objective of accomplishing OWS. The mechanism is started by the absorbance of photons, as seen in the center of Fig. 2e. When radiation is absorbed, a VB generates exciting holes, and a CB generates exciting electrons. This process occurs within a femtosecond period. When a quick release process occurs within femto- to picoseconds, an excited state (consisting of electrons/holes) is divided into free carriers. The surface layer of materials then directs the electrons/holes towards the HER and OER catalysts, thereby typically within the range of nano- to microseconds. Fig. 2f depicts a six-gear idea illustrating the successive occurrence of the PWS reaction at multiple intervals. Photon absorbance triggers irregular photo-physiochemical reactions. The photon absorbance results in the formation of stimulation, which is the activation of a single electron from the VB to the CB. The possibility of occupying these positions is mostly governed by the electronic framework of semiconductors, namely the spatial migration of particles.⁶⁵

Due to the strong electronegativity of oxygen atoms, conventional PWS employs transition metal oxides to generate stable compounds.⁶⁶ These oxides are classified into two groups based on the configuration of their d orbitals. Titanium (Ti), vanadium (V), niobium (Nb), and tungsten (W) possess a low VB energy as a result of their insufficiently occupied d orbitals. Furthermore, the oxygen 2p orbitals significantly impact their VB, resulting in materials with large band gaps and inefficient photocatalytic activities. Various methods have been applied to improve their light-absorbing efficiency, including doping and defect formation. For example, Bo Yan *et al.*⁶⁷ used high-temperature hydrogenation to make defect-enriched black TiO₂, which showed outstanding photocatalytic activity for the HER (Fig. 3a). In contrast, Co, Mn, Fe, and Ni have occupied d orbitals, and their oxides have small band gaps and strong d-d transitions. Iron(III) oxide (Fe₂O₃) is a typical example of this category due to its abundance and low cost.⁶⁸ However, a drawback of transition metal oxides is their low conductivity. To overcome these constraints, multiple metal oxides have been designed. Besides, the photocatalytic activity of metal nitrides and metal sulfides has also been boosted. Bismuth vanadate (BiVO₄) is a commonly studied ternary oxide with extensive research on its photocatalytic activity.^{69–71} The electronic conductivity of BiVO₄ can also be improved by mixing it with cations such as Ag⁺, V₅⁺, and W₆⁺, resulting in enhanced catalytic activity as depicted in Fig. 3b.⁷² Other ternary oxides that can alter the band gap are CuWO₄, ZnFe₂O₄, CaFe₂O₄, CuBi₂O₄, and CuNb₃O₈.^{73–76} The combination of nitrogen substitution with metal doping may reduce the band gap resulting from elevated 2p orbital energy levels. Reports indicate that the VBs of sulfur and selenium, which are located at higher energy levels, might generate materials with shorter energy gaps than oxides. These energy gaps are similar to those of nitrogen.^{77,78} The higher-lying p bands of sulfur and selenium, like nitrogen, generate materials with narrower band gaps than oxides.^{79–81} Photoactive materials have been synthesized using silicon, III-V semiconductors, and carbon-based compounds.^{82–84} Aside from the turnover frequency (TOF), the photocatalyst material,



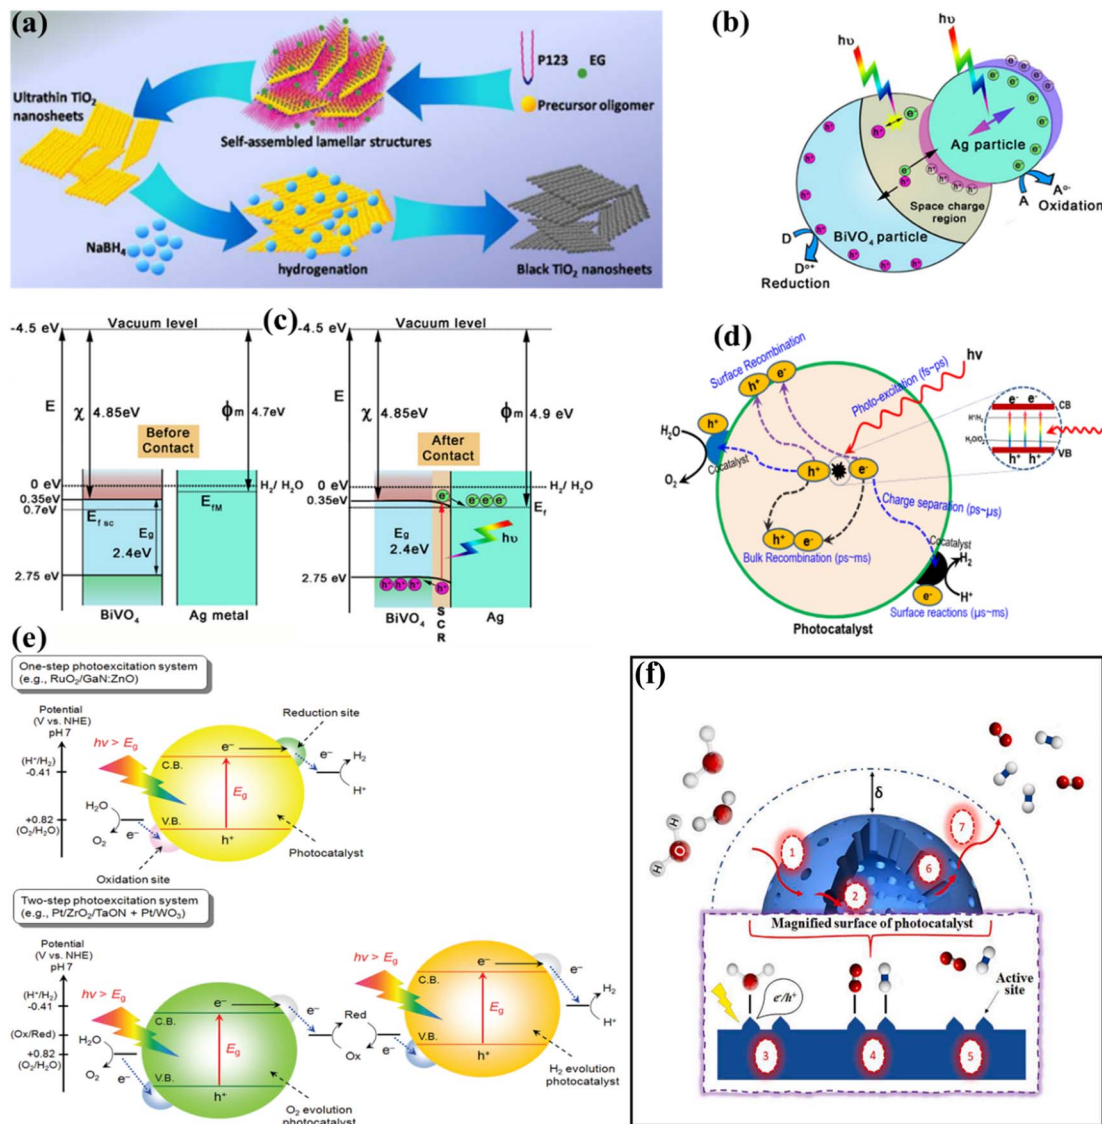


Fig. 3 (a) Schematic of the synthesis of the ultrathin black TiO₂ nanosheets. Adapted from ref. 67. Copyright © 2016, Royal Society of Chemistry, (b and c) schematic illustration of the photocatalytic mechanism of the Ag/BiVO₄ M-SC nanocomposite photocatalyst: the showing space charge area due to plasmonic action and band bending with aligned Fermi levels (b and c). Adapted from ref. 72. Copyright © 2016, John Wiley and Sons, (d) basic principles of PWS using semiconductors. Adapted from ref. 85. Copyright © 2017, Elsevier, (e) schematic representation of PWS via one-step and two-step photoexcitation. Adapted from ref. 88. Copyright © 2010, American Chemical Society, (f) seven catalytic steps involved in heterogeneous PWS. Adapted from ref. 44. Copyright © 2021, Elsevier.

stability, and light source should all be considered. As a result, the HER should not be the primary means of evaluating the system performance of the photocatalyst material. The electron-hole pairs are generated at the catalyst surface to catalyze WS and therefore the critical issue in this process is electron and hole recombination.⁵²⁻⁵⁴ During photogeneration, electron-hole pairs can immediately recombine before activating redox reactions that yield photons or heat energy. Electrons and holes are more likely to recombine before photocatalysis due to surface defects, which can lower the photocatalytic activity. In general, several defects and smaller particles impede electron and hole recombination, as shown in Fig. 3c.⁸⁵ Surface defects are reduced in high crystallinity and stoichiometry materials, which enhances the WS reaction. Due to the small diffusion




pathways provided by nanoparticles, recombination is reduced. Charge carriers can interact effectively with surface-active sites because small particles have a large surface area (SA). The reaction between electrons and holes at active sites results in the generation of H₂ and O₂ sources. The intrinsic activity and number of active sites on the surface significantly impact this phase. The reaction won't proceed even if the electrons and holes reach the surface if there aren't enough active sites available. Since the lowest CB values in many transition metal oxides are negative, co-catalysts such as precious metals and nickel oxide are required to initiate the HER.⁵² However, assuming that the VB of the metal oxides is sufficiently positive, in that case, water can be oxidized to O₂ without co-catalysts (Fig. 3d). Particle size and crystallinity are also essential for the



WS reaction because they provide more accessible active sites and SA for high activation. Unlike other processes such as dye degradation, the adhesion of the reactant water molecules in WS is insignificant. Although converting WS to H₂ and O₂ is not thermodynamically beneficial due to the large energy requirements, a reverse reaction is more feasible. Therefore, separating and removing the generated H₂ and O₂ sources is crucial.

1.3. Thermodynamics of photocatalytic water splitting

From a thermodynamic perspective, the process of converting WS into H₂ and O₂ represents an endothermic reaction. Eqn (1) demonstrates that a typical Gibbs free energy shift ΔG^0 of +237 kJ mol⁻¹ is required.



$$\text{Band gap } (E_g, \text{ eV}) = 1240/\lambda(\text{nm}) \quad (4)$$

To accomplish a thermodynamic non-spontaneous process using photocatalysis, additional energy from photons, above from 1.23 eV potential barrier, must be supplied to the interaction by the catalysts. This potential is subsequently transformed into chemical energies in the resulting molecules. Hence, the catalyst must possess an energy gap (E_g) that exceeds 1.23 eV to accomplish WS. This implies that its absorption edge wavelengths (λ) should be less than 1000 nm, as stated in eqn (4). To comprehend the visible spectrum, its energy must be less than 3.0 eV, which corresponds to an absorbing border wavelength of more than 400 nm, as stated in eqn (4). In addition, to enhance the oxidation and reduction process of H₂O through photoinduced electron and hole pairs, it is necessary to align the band alignment of the catalysts with the redox capability of water. To provide the motoring effect for the oxidations/reductions of water, the CB of the photocatalyst ought to possess a higher negative perspective than the reduction capability of H⁺/H₂ (0 eV vs. NHE, pH = 0), whereas the VB ought to have a more positive perspective than the oxidation perspective of O₂/H₂O (1.23 eV vs. NHE, pH = 0). It is important to observe that the band boundaries of the semiconductor catalyst typically show a pH dependent status (as shown in eqn (5)). Additionally, the redox capacities of water also demonstrate an inverse pH dependency with a slope of 0.059 V pH⁻¹. Consequently, there is no variation in the overpotential of photoexcited electrons for water redox at various pH levels.^{86,87}

$$E_{\text{CB}} = E_{\text{CB}}^0 (\text{pH} = 0) - 0.059 \text{ pH} \quad (5)$$

1.4. Surface phenomena of photocatalysts during water splitting

When seen as a solid–liquid heterogeneous reaction, compressive WS has seven essential steps (as shown in Fig. 3e). The start of the

surface reaction needs the diffusion of H₂O molecules over the solid–liquid surface, allowing them to reach the external surface of photocatalysts, as shown in step 1 of Fig. 3e. The thickness of the boundary layer determines the rate of convective diffusion rate (δ) and it is commonly increased as this layer becomes thinner due to uncertain mixing. Besides the exterior surface, the interior surface, which is determined by its porosity, is also significant in addition to the outwards, because the pores of the photocatalyst can contain substantial active sites. Therefore, this study also considers the internal diffusion (step 2) to determine how H₂O is transported from the exterior to the interior surface. However, due to the nanoscale dimensions of the pores, disturbances in the reaction substrate have not been regarded as significant in the current phase. Historically, the development of nano-sized photocatalysts has focused for optimizing internal diffusion and maximizing SA to facilitate efficient WS. The sequence of steps (3, 4, and 5) depicted herein demonstrates the surface reaction, wherein H₂O molecules are adsorbed onto the active sites, followed by their transport through diffusion. Subsequently, the water molecules dissociate into H₂ and O₂, and the resulting products are released from the active sites, completing the WS cycle. The process of WS relies on the utilization of the electron–hole pair formed during photo-absorption, which is dependent upon the specific characteristics of the photocatalysis involved. Following the completion of the surface reaction, the desorbed products are subsequently transported through diffusion in the opposite direction (steps 6 and 7). During the concluding phase, the gaseous products are discharged as a collective mass. Fundamentally, the phases depicted in Fig. 3f are sequential and overlapping. In the context of photocatalysis, it is critical to enable quick recharging and WS molecules at active sites (steps 3 and 4, respectively) to efficiently inhibit undesired charge recombination. This is crucial due to the highly reactive nature of the photogenerated charge species. Similarly, the rapid desorption of H₂ and O₂ (as described in step 5) is critical in preparing the currently occupied active sites for successive cycles of reactions. The kinetics of these processes also depend on the diffusional transport explained in stages 1, 2, 6, and 7, respectively. Consequently, the overall rate of PWS will slow down.

1.5. Quantum efficiency and solar-to-hydrogen efficiency

The phenomenon of quantum yields, which refers to the frequency whereby molecules act like photons taken during a specific time, is a key concept in the field of photocatalysis. Photocatalytic researchers regularly measure the quantum efficiencies of reagent degradation, product formation, photon emissions, and various other photochemical reactions and photophysical phenomena that take place in photochemical processes.⁸⁹ In the field of heterogeneous photocatalysis, quantum yield has been employed to measure the ratio of reacting electrons to the entire quantity of photons that integrate the system during the reaction. This measurement is performed without considering the specific reaction symmetry or the type of irradiation deployed. It differs from the normal measurement in uniform photochemistry, which focuses on the quantity of



consumed photons at a specific wavelength. The quantum yield in heterogeneous systems may be determined using an identical approach as for conventional photochemistry, provided that the quantity of consumed photons or the proportion of photons captured by the solid-state photocatalyst can be measured. Due to the substantial dependence of the performance of photocatalysts on experimental situations such as light quantity and reaction temperatures, comparing the functions of different catalysts can prove challenging.⁹⁰ It is important to emphasize that the real quantum yield must be compared to the interior quantum efficiency (IQE), which is determined by dividing the number of reacting electrons by the number of absorbed photons. The measurement of the quantity of photons captured by a particle-

based catalyst in a dispersion environment is challenging due to the phenomena of light dispersion and losses. To get a 100% IQE, every single photoinduced electron must relocate to surface reaction locations before performing bulk mixing. Furthermore, the HER must encompass the insertion of two electrons, while the OER requires the insertion of four holes. These infusions must take place sequentially with no reverse charge movement. Nevertheless, the scarcity of WS demonstrations with an exterior quantum efficiency (EQE) of over 50% is mostly attributed to the numerous possibilities for reverse transmission of electrons, despite the deployment of catalysts sensitive to UV light. Strontium titanate (SrTiO₃) is an appropriate material for evaluating the feasibility of this option in photocatalysis. This material is



Fig. 4 (a) Time function for PWS; (b) the provided data include the ultraviolet-visible DRS of untreated SrTiO₃:Al (shown by the black solid line) and the relationship between wavelengths and EQE throughout WS on Rh. Adapted from ref. 99. Copyright © 2020, Springer Nature, analysis of efficiency and study of mechanisms. (c) The effectiveness of the Rh/Cr₂O₃/Co₃O₄-InGaN/GaN NWs varies with temperatures. (d) This experiment aims to determine the stability of the Rh/Cr₂O₃/Co₃O₄-coated InGaN/GaN nanowires. (e) The recombination process between H₂/O₂ depends on temperatures. (f) Free-energy pattern that shows the process of H₂/O₂ mixing on the cocatalysts Co₃O₄, Rh, and Cr₂O₃. Adapted from ref. 98. Copyright © 2023, Springer Nature.



a highly investigated catalyst with a band gap of 3.2 eV.^{91,92} Throughout decades, its efficiency for WS can be enhanced up to 69% by several improvements.^{93,94} By selecting and placing highly reactive cocatalysts for the HER and OER on SrTiO₃:Al particles, researchers were able to maximize the EQE to its highest achievable value. The achievement was attained by employing a sequential photo-deposition technique rather than an impregnating approach, leading to the uncontrolled distribution of the co-catalysts. Fig. 4a demonstrates the WS capability of SrTiO₃:Al, which has been enhanced by loading it with Rh, Cr, and Co particles as co-catalysts. These co-catalysts were incorporated using alternative photo-deposition or traditional impregnating techniques. The photocatalyst, including 0.1 wt% of Rh and later 0.05 wt% of Cr₂O₃, performed a two-phase photodeposition process. As a result, it produced H₂ and O₂ in the predicted stoichiometric proportion for WS.⁸⁸ The WS efficiency reached its maximum level when the concentrations of Cr and Co were both 0.05 wt% (Fig. 4b). The main difficulties confronting POWS are primarily associated with the narrow spectrum of visible light sources that can be utilized, the significant recombination of electron-hole pairs generated by light, the significant potential required for surface catalysis, and the undesired recombination of H₂ and O₂ produced through conventional photocatalysts. These issues result in a relatively low STH (typically less than 3%) in the majority of the mentioned photocatalytic systems.^{95,96} The spectrum of light wavelengths to which a photocatalyst may respond determines its greatest possible performance in WS into H₂ and O₂, known as the computational optimum STH efficiencies. In recent years, researchers have successfully developed indium gallium nitride (InGaN)/gallium nitride (GaN) nanowire (NW) catalysts with precise manipulation of conventional silicon wafers. These catalysts exhibit good crystalline structure and have demonstrated a broad band of sensitivity to visible illumination (400–700 nm), making them acceptable for OWS applications with appropriate band-edge possibilities.⁹⁷ In this study, Zhou *et al.*⁹⁸ presented an apparent temperature-sensitive recombine phenomenon of H₂ and O₂ in POWS on Rh/Cr₂O₃/Co₃O₄-loaded InGaN/GaN NWs. Based on the results of this study, researchers have determined an approach to reaction that is highly efficient. They effectively showed that the POWS response has a performance of approximately 9.2% due to the improved forward H₂/O₂ formation response and the suppressed H₂/O₂ replication response at an ideal interaction temperature of around 70 °C. Furthermore, by following this approach, a significant STH performance of 6.2% was attained on a substantial photocatalytic OWS system (Fig. 4c–f).

2. Photocatalytic reactions

2.1. Reaction types

2.1.1. Photochemical reactions. Heterogeneous PWS relies on three essential components: a sacrificial electron donor, a catalyst, and a visible light absorber. Even though the fundamental principles of photochemical and photoelectrochemical systems are identical, their structural configurations differ. In photochemical processes, the WS reaction happens at the surface between an electrolyte and a semiconductor as shown in Fig. 5a. A

voltage is needed at the semiconductor-liquid junction for WS to occur. For the semiconductor to be compatible with the electrolyte and avoid corrosion, it must be electrolyte-friendly. The type of product produced, whether it is H₂, O₂, or OWS depends on the position of the semiconductor band edge.^{100,101}

2.1.2. Photo-electrochemical reactions. When a semiconductor photocatalyst is illuminated under UV-visible light having energy equal to or exceeding the band gap of semiconductors, WS occurs, as illustrated in Fig. 5b. The photocatalyst absorbs the energy from the incident light, leading to the separation of charges, specifically electrons and holes, within the VB and CB. Within the CB, photogenerated electrons stimulated by light contribute to the conversion of absorbed H⁺ into H₂, whereas holes oxidize water near the surface of the CB. Depending on the process, semiconductors can be used as either the photocathode or photoanode in PWS. To carry out the entire reaction, a semiconductor electrode must come into contact with a redox pair in PEC WS. This method of illuminating the cathode or anode produces enough voltage for WS. In PEC WS, the reaction is carried out by two separate electrodes.^{102–104}

2.2. Reaction setup

Researchers frequently use experimental setups that include a vacuum pump, a gas chromatograph detector reaction cell, and a gas circulation pump. The quantitative measurements of O₂ and H₂ production can be determined using O₂ and H₂ sensors, as well as volumetric methods. To ensure precise measurement of the produced O₂, it is essential to eliminate the reaction solution with inert gases before testing, ensuring that the setup is entirely free of air. Various light sources are utilized to initiate the reaction, such as high-pressure mercury lamps combined with a quartz reaction cell for UV-responsive photocatalysts or a 300 W xenon lamp in conjunction with an optical filter for catalysts with band gaps less than 3 eV (Fig. 5c). Additionally, to investigate the generation of solar H₂, researchers can utilize a solar simulator. Within the literature, various types of response cells have been documented, including those involving two semiconductors during the 1970s and 1980s, as well as single-junction cells that are recognized as the driving force behind the HER.^{63,105} However, their low photovoltaic power output is insufficient for efficient OWS. To enhance the WS process, researchers have explored the combination of multi-junction devices and electrocatalysts. A recent study achieved an efficiency of 4.7% by utilizing a monolithic three-junction amorphous silicon solar cell in conjunction with cobalt phosphate and a nickel, zinc, and molybdenum tri-metal catalyst.¹⁰⁶

3. Photocatalytic conditions

The photocatalytic activity of inorganic catalysts is influenced by several factors, including surface chemistry, junction gaps, particle size and shape, crystallinity, band edge positions, doping, and the depth of entrapment.¹⁰⁸ To minimize these factors, various techniques such as hydrothermal, microwave-assisted, surfactant-assisted, and sonochemical synthesis are needed to synthesized photocatalysts.^{109–112} The fabrication technique has



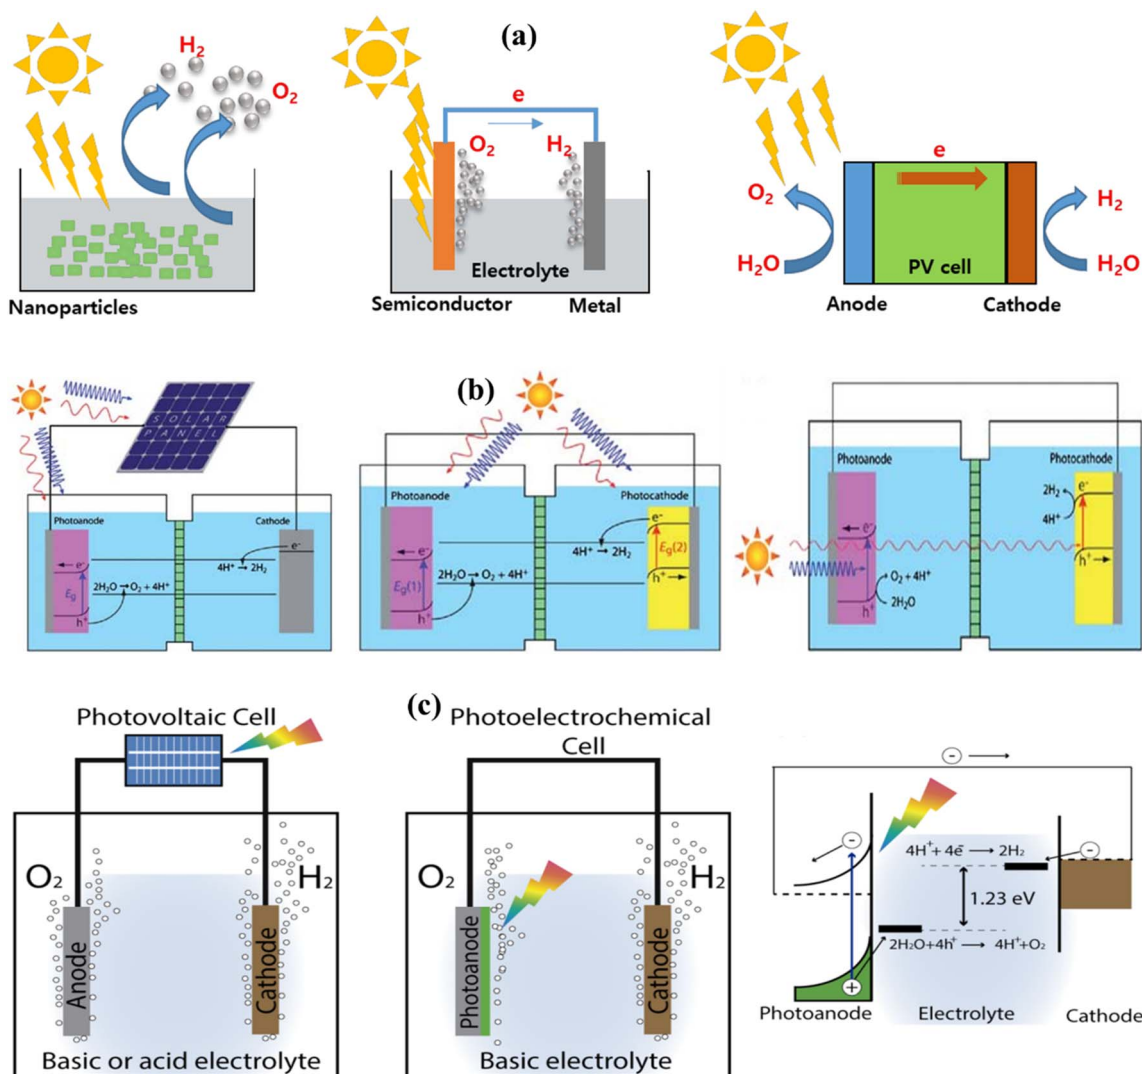


Fig. 5 (a) Solar H₂ solutions using a WS containing particulate PWS system, PEC WS system, and photovoltaic–photoelectrochemical hybrid (PV–PEC) system. Adapted from ref. 85. Copyright © 2017, Elsevier, (b) general illustration of PEC. Adapted from ref. 102. Copyright © 2010, Royal Society of Chemistry, (c) solar-driven electrochemical WS cells based on a photovoltaic–electrolysis cell and photoelectrochemical WS cell and the working principle of WS PEC with an n-type semiconductor photoanode. Adapted from ref. 107.

a substantial impact on catalytic activity, especially when structurally active nanoparticles and large SA complexes are utilized. Factors, such as temperature, surfactants, concentration, and pH value, influence the size, shape, and structure of catalysts. The concentration of developing elements in solution influences the nucleation and crystal formation, affecting the activity.¹¹³ Co-catalytic systems such as copper oxide and zinc oxide nanowires with a core–shell structure,¹¹⁴ copper/copper oxide heterojunctions with nickel decoration, Fe₂O₃ nanorod/MgFe₂O₄ heterojunctions with three-dimensional (3D) cobalt branching,¹¹⁵ and TiO₂ anatase combined with copper oxide, have been developed and studied extensively (Fig. 6a).¹¹⁶ The pH value, as well as the hydrothermal temperature, duration, and solvent ratio, all affect the morphology of inorganic photocatalysts.^{117,118} The geometry of nanostructures in BiVO₄ is dramatically altered when the volume ratio of ethylene glycol to water (EG/H₂O) is changed from 10/50 to 60/0. The FE-SEM images show lamellar morphologies at 10/50

and 20/40, with 20/40 resulting in thicker sheets. Morphologies resembling leaves, bowknots, sweets, and olives were formed at 30/30, 40/20, 50/10, and 60/0. This is because the increased viscosity and inhibitory effect of EG on crystal formation allow nanocrystals to spin and seek a 3D structure to stabilize them. The morphology of BiVO₄ is pH-dependent and ranges from irregular microparticles to hollow microspheres.¹¹⁸

3.1. Surface and band structure

Numerous investigations have demonstrated that the chemical characteristics, morphology, and local structure of the catalyst surface play a crucial role in influencing the photocatalytic activity of WS reactions. Chemically modified surfaces are frequently used to improve catalytic activity by reducing corrosion, deactivating undesirable surface states, changing band-edge locations, or selective carrier removal.^{66,119} However, it's



important to note that the surface also governs the trade-off between light absorption and carrier diffusion lengths. Increasing the SA may lead to reduced photovoltage and an increase in surface recombination. As a result, before implementing any surface modifications, an in-depth comprehension of the loss pathways must be acquired.¹²⁰ CuO with sheet-like morphologies absorbs less sunlight than Cu with spherical morphologies. As the size of the crystallite decreases, the band gaps also reduce.¹²¹ BiVO₄ is a recent example that has attracted researchers due to its narrow band gap (2.4 eV) and diverse possible morphologies (Fig. 6b–i). Control, suitable structures, and BiVO₄ geometry are necessary for photocatalytic performance.¹²² The photocatalytic performance of BiVO₄ varies depending on the specific facets that are exposed.¹²³ These facets include single crystal microspheres,¹²⁴ octahedral and decahedral nanoplates,¹¹⁷ peanut- and needle-like nanoplates,¹²⁵ spindly hollow microtubes,¹²⁶ leaf,¹²⁷ hyperbranched,¹²⁸ flower-like,¹²⁹ porous olive,¹³⁰ and fusiform.¹³¹ Additionally, various shapes of BiVO₄ coated with CeO_x nanodots,¹³² BiVO₄/TiO₂ nanofibers,¹³³ Bi₂WO₆/BiVO₄ composites,¹³⁴ monoclinic BiVO₄/surface rough TiO₂ ceramic fibers,¹³⁵ and m-BiVO₄/001-TiO₂ heterojunctions have been studied for their photocatalytic performance.¹³⁶ Band gap engineering is

a successful strategy for enhancing photocatalytic performance.¹³⁷ Assuming that A and B are the junction materials, there are three types: Type 1, where the A material with a higher CB than a material with a lower VB is considered more stable. The natural tendency of electrons and holes to move downward and upward in the direction of lower energy allows them to accumulate in material A. The VB and CB values of material A are less than those of material B, causing charge carrier separation. Type III and Type II junction materials have different CB and VB properties.¹³⁸ The Type II junction architecture is frequently employed in the fabrication of photocatalyst heterojunctions.¹³⁹ Charge carrier separation enhanced the activity of CdS/TiO₂ and CdS/ZnO heterostructures.^{140,141} Junction films must be nanostructured to facilitate efficient charge transfer. It is proposed to use a thin layer with charge carrier diffusion to absorb significant amounts of light.⁶⁶ Using nanostructured BiVO₄/WO heterojunctions, near-theoretical photocurrent generation has been realized.¹⁴² According to a recent study, photocathodes may carry out the water reduction reaction step in a PEC cell using molecular beam epitaxy and band gap engineering approaches. A layer of SrTiO₃, 4 nm thick, is a protective layer for silicon and a charge transport tunnel junction. The coupling of a p-type silicon substrate and a SrTiO₃



Fig. 6 (a) Depiction of the photocatalysis mechanism at the TiO₂/Cu₂O heterostructures, and a suggested model for the formation of negative oxygen ions on wood treated with TiO₂/Cu₂O under UV light. Adapted from ref. 116. Copyright © 2016, Springer Nature, (b–i) morphology of BiVO₄.¹⁴⁴ This chapter is distributed under the terms of the Creative Commons Attribution 3.0 License.



lattice results in a defect-free surface and low defect density. A photocurrent density of 35 mA cm^{-2} was attained using 100 mW cm^{-2} broad-spectrum light and a 450 mV open-circuit voltage.¹⁴³

4. The importance of developing visible-light-driven water splitting systems

Since 1980, several UV light-driven WS systems have been proposed.^{145–148} SrTiO_3 is an important photocatalyst that works under UV light irradiation. Recently, Al-doped SrTiO_3 has been reported to display relatively improved stability and efficiency.^{93,149–151} However, the production of H_2 gas through this process is challenging as the STH values of that system do not match the threshold value achieved with fossil fuels.⁹⁹ These low values are because the solar spectrum comprises only approximately 5% of UV light (*i.e.*, wavelengths below 400 nm). In contrast, visible light ranges from 400 to 800 nm and constitutes 50% of the total solar spectrum. Hence, employing a photocatalyst capable of using incident solar radiation below 600 nm can provide an STH close to 16% with 100% efficiency.¹⁵² For this reason, photocatalysts working at long wavelengths are very efficient in the renewable H_2 production process.¹⁵³

4.1. One-step-excitation visible-light-driven overall water splitting

The application of photocatalysts for one-step excitation in visible-light-driven WS poses significant thermodynamic challenges. Firstly, the band gap energy of the selected photocatalyst must be less than 3.1 eV to ensure the optimal absorption of visible light radiation. Secondly, photocatalysts with narrow band gap energies tend to exhibit low driving forces and limited stability. This is primarily attributed to the reduced potential difference between the valence band maximum (VBM) of photocatalysts concerning the water oxidation potential and the conduction band minimum (CBM) concerning the water reduction potential. As a result of the photogenerated carrier concentration, the photocatalytic materials photo corrode faster. Third, photocatalysts with small band gaps are not well positioned about the redox potentials of water. Thermodynamically, the HER and OER potentials of water should be supported by the CBM and VBM of the photocatalyst for efficient POWS simultaneously. Fourthly, narrow band gaps possessing photocatalysts are likely to be oxidized during the oxidation reaction of water, since they typically consist of N_3^- and S_2^- anions; therefore, considering the above-stated reason, only a limited number of photocatalysts meet this criterion for use in one-step-excitation for visible light-induced WS reactions. Alternatively, attention has been given to the utilization of photocatalysts that respond to visible light in the half-reactions of the HER and OER in the presence of sacrificial electron donors and acceptors, respectively.^{154–162} Since the bottom of the CB is at a possibility that is greater than the H^+ to H_2 reduction capacity ($0 \text{ V vs. NHE at pH} = 0$), then the electrons/holes

produced by light and holes can reduce H^+ and oxidize H_2O , accordingly. Furthermore, as shown in Fig. 7a, the highest level of the VB needs to be situated at a stage that is significantly more positive than the $\text{H}_2\text{O} \rightarrow \text{O}_2$ oxidation capacity ($1.23 \text{ V vs. NHE at pH} = 0$).¹⁶³ Conversely, the HER cannot produce renewable H_2 on its own due to its reliance on chemical energy derived from sacrificial reagents, often produced by using fossil fuels. Consequently, this process has limited or no direct utilization of solar energy. Hence, it is imperative to establish a comprehensive WS system that operates without the need for sacrificial reagents. Since the year 2000, many photocatalysts responding to visible light for one-step OWS have been reported.¹⁶⁴ Notably, the solid solution of $\text{Ga}_{1-x}\text{Zn}_x\text{N}_{1-x}\text{O}_x$, which can adjust its absorption edge to encompass wavelengths up to 500 nm by altering the component ratio^{165–167} has enhanced its apparent quantum efficiency (AQE) to 5.1% at 410 nm .¹⁶⁸ A subsequent study also found that a low concentration of palladium (Pd) was effective in this context.¹⁶⁹ Transition metal oxynitrides and nitrides, such as Ta_2O_5 , TaON , and Ta_3N_5 , have garnered considerable attention due to their high light-absorption properties.¹⁷⁰ In particular, Ta_3N_5 is well-suited for the OER, because it can produce H_2 or O_2 from aqueous solutions containing sacrificial electron donors or acceptors, all while absorbing visible light up to 600 nm .¹⁷¹ Nevertheless, due to substantial charge recombination at defects, the achievement of OWS remained difficult until 2018. Rapid growth has recently been used to generate Ta_3N_5 single crystal nanorods with no grain boundaries and cubic KTaO_3 particle edges that are lattice-matched.¹⁷² Upon the introduction of a $\text{Rh/Cr}_2\text{O}_3$ cocatalyst, these single-crystalline Ta_3N_5 nanorods exhibited the ability to split water into HER and OER products in a stoichiometric ratio of 2 (Fig. 7b and c). In one-step excitation OWS systems, $\text{LaMg}_x\text{Ta}_{1-x}\text{O}_{1+3x}\text{N}_{2-3x}$ ($x^{1/3}$) has also been used. The composition of this material can be changed to produce a variety of solid solutions with different band gaps and positions. The OWS was accomplished in 2015 utilizing $\text{Ta}_2/\text{3O}_2\text{N}$ at wavelengths up to 600 nm after the inclusion of a RhCrO_y cocatalyst and layers of amorphous titanium and silicon oxyhydroxide to regulate surface redox processes. Following that, the photocatalyst, cocatalyst species, and coating materials were optimized, resulting in a significant increase in photocatalytic activity during WS.¹⁷³ For example, changing the Mg and N contents of a solid solution led the VBM to shift to a more positive potential, facilitating water oxidation. Another study employing $\text{LaSc}_x\text{Ta}_{1-x}\text{O}_{1+2x}\text{N}_{2-2x}$ ($x_{0.5}$) reached OWS as a result of this adaptation. Despite these advancements, the AQE values and stability of these oxynitride and nitride photocatalysts remain low, requiring further improvements in crystallinity, particle shape, and surface modifications. Intense visible light absorption has also been observed in metal chalcogenide photocatalysts, such as cadmium sulfide (CdS), which has a band gap value of 2.4 eV and is suitable for general WS. Extensive research on the HER half-reaction has been conducted using this photocatalyst.¹⁷⁴ CdS has been employed as a photocatalyst to enable the visible-light-driven OER with the support of surface modifications. In this approach, Pt serves as a reduction cocatalyst and $\text{Ru}(\text{tpy})(\text{bpy})\text{Cl}_2$ acts as an oxidation cocatalyst.¹⁷⁵



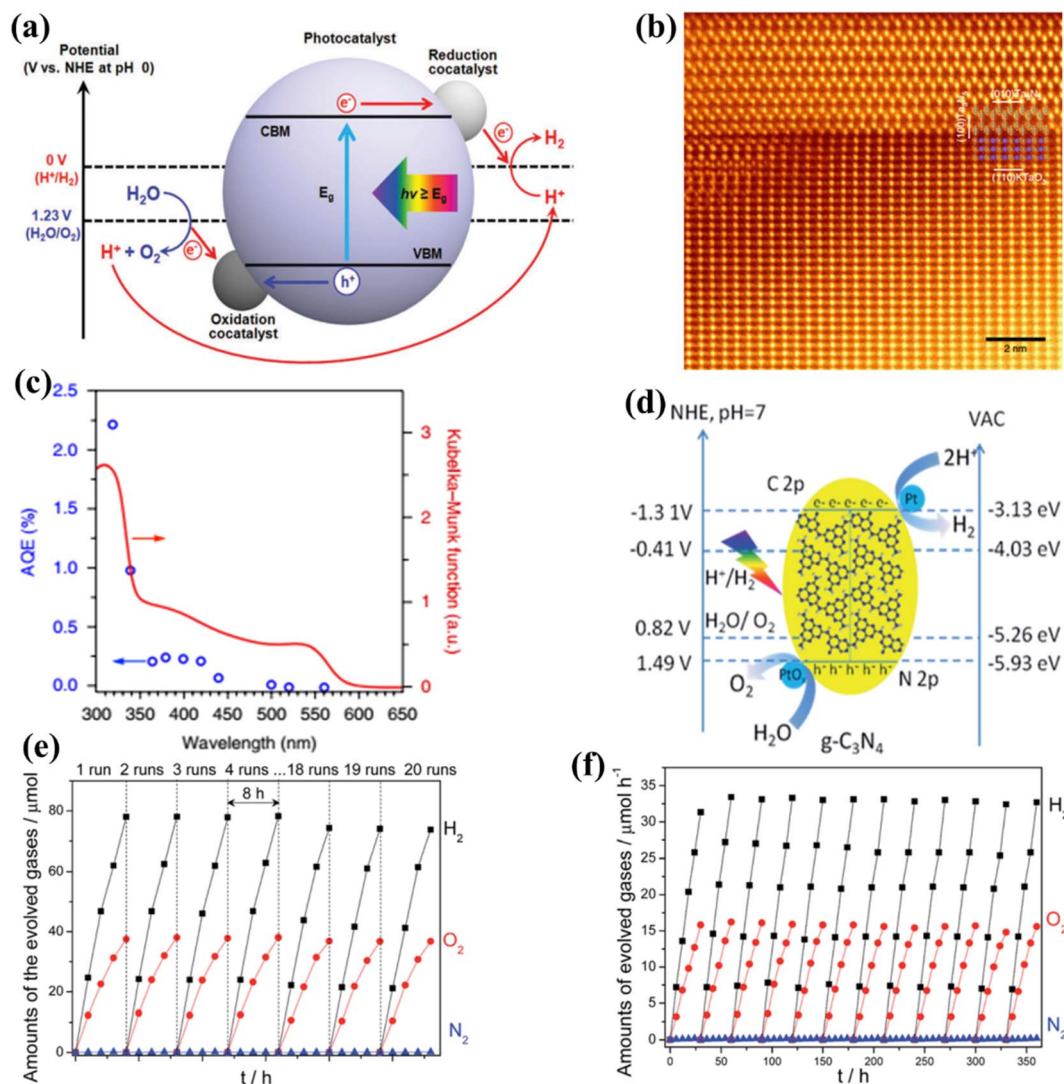


Fig. 7 (a) Illustrations showing the conceptual potential of the one-step stimulation of OWS on particulate catalysts. Adapted from ref. 163. Copyright © 2019, Royal Society of Chemistry, (b and c) colored annular dark-field STEM image of $\text{Ta}_3\text{N}_5/\text{KTaO}_3$, along with the apparent AQE as a function of the incident light wavelength.¹⁷¹ (d–f) The band positions of PCN and the WS activity under visible light irradiation. Abbreviations: NHE, normal hydrogen electrode; VAC, vacuum. Adapted from ref. 184. Copyright © 2016, Royal Society of Chemistry.

Oxysulfide photocatalysts are gaining popularity due to their enhanced stability compared to chalcogenides, all while maintaining effective performance at longer wavelengths. These characteristics are attributed to the hybridization of O 2p and S 3p orbitals within these materials. Initial research demonstrated promising catalytic activity of $\text{Sm}_2\text{Ti}_2\text{O}_5\text{S}_2$, which absorbs wavelengths shorter than 650 nm, for both the HER and OER half-reactions, indicating suitable band positions for OWS.^{176,177} Since the development of OWS with this material utilizing single-step excitation has not yet been reported, further study has focused on improving the production, particle shape, and surface characteristics of this oxysulfide molecule.^{178,179} A band gap of roughly 1.9 eV is achieved by substituting samarium with yttrium in a solid-state process, resulting in an absorption edge at 650 nm. This specific

oxysulfide compound, $\text{Y}_2\text{Ti}_2\text{O}_5\text{S}_2$, demonstrated the capability for OWS within a 20-hour reaction period when the HER and OER were facilitated by cocatalysts $\text{Rh}/\text{Cr}_2\text{O}_3$ and IrO_2 , respectively.¹⁸⁰ Recently, there has been a growing interest in exploring conjugated polymers that exhibit band structures similar to semiconductors as potential candidates for POWS. Prior studies predominantly concentrated on investigating polymeric carbon nitride (PCN) for photocatalytic half-reactions.^{181–183} After much effort, OWS under both UV and visible light was achieved by loading appropriate cocatalysts onto PCN (Fig. 7d–f).^{184–186} In addition, the utilization of traditional cocatalysts, such as single-site cocatalysts, has displayed a notable enhancement in performance. Furthermore, 1,3-diyne-linked conjugated microporous polymer nanosheets (CMPNs) have been synthesized through the oxidative coupling of terminal alkynes.¹⁸⁷



These materials have been found to serve as versatile photocatalysts for overall water splitting when exposed to visible light.¹⁸⁸

4.2. Two-step-excitation visible-light-driven overall water splitting

Certain photocatalysts, which respond to visible light, can only be employed for one-step excitation in OWS due to a misalignment between their energy bands and the redox potentials of water. To address this challenge, a two-step-excitation OWS, commonly referred to as Z-scheme WS, has been devised. In this system, photocatalysts are employed for both the HER and the OER, with electron mediators used to prevent the accumulation of excess holes or electrons in each photocatalyst.¹⁸⁹ This approach significantly broadens the range of usable photocatalysts, as long as the HER and OER catalysts satisfy the thermodynamic conditions for the corresponding WS half-reactions. The Z-scheme WS systems have been extensively explored using reversible donor/acceptor coupling driven by visible light.^{190,191} For instance, PtO_x/WO_3 and IO_3^-/I^- pairings were used as the OER and redox mediator, respectively, while barium-modified Ta_3N_5 was employed as the HER catalyst.¹⁹² Another Z-scheme WS system was synthesized using ZrO_2/TaON as the HER catalyst and Pt/WO_3 as the OER catalyst, achieving an AQE of 6.3% at 420 nm.¹⁹³ The AQE value was further improved to 6.8% using $\text{MgTa}_2\text{O}_{6-x}\text{N}_y/\text{TaON}$ as the HER catalyst and PtO_x-WO_3 as the OER catalyst, although the resulting STH value was low (around 3).¹⁹⁴ The hydrogen evolution reaction (HER) in Z-scheme WS system has been successfully demonstrated with $\text{Sm}_2\text{Ti}_2\text{O}_5\text{S}_2$, an oxysulfide photocatalyst, coupled with WO_3 serving as the oxygen evolution reaction (OER) catalyst and the I_3/I^- redox pair functions as an electron mediator shuttle in this configuration. Additionally, a photocatalytic system based on the Pt/NiS-supported $\text{La}_5\text{Ti}_2\text{AgO}_7\text{S}_5$ photocatalyst as the HER catalyst achieved an AQE of 0.12% at 420 nanometers.¹⁹⁵ Other oxysulfide photocatalysts, such as $\text{La}_5\text{Ti}_2\text{CuO}_7\text{S}_5$ and $\text{La}_6\text{Ti}_2\text{O}_5\text{S}_8$, have been found to evolve H_2 and O_2 , despite oxygen being typically produced in a stoichiometric proportion in these systems. Recently, a WS Z-scheme has been developed using $\text{HfCa}_2\text{Nb}_3\text{O}_{10}$ nanosheets with a Ru(II), tris-diimine type photosensitizer as the HEP, $\text{PtO}_x/\text{H-Cs-WO}_3$ as the OEP, and I_3^-/I^- as the redox mediator (Fig. 8a).¹⁹⁶ By modifying the OWS with amorphous Al_2O_3 clusters, the AQE at 420 nm was increased to 2.4%. This is the highest AQE for an OWS system based on a dye-sensitized photocatalyst ever reported. PCN materials can be used as HER catalysts in Z-scheme WS systems, with BiVO_4 or WO_3 as the OEP and the electron mediator I_3^-/I^- . Another common redox mediating pair is $\text{Fe}_3^+/\text{Fe}_2^+$. A Z-scheme system was synthesized in one study using oxchloride $\text{Bi}_4\text{-NbO}_8\text{Cl}$ as the visible-light-responsive OEP and $\text{Ru}/\text{SrTiO}_3\text{:Rh}$ as the HER catalysts, along with a $\text{Fe}_3^+/\text{Fe}_2^+$ redox mediator, which produced H_2 and O_2 under visible light radiation. Bismuth tantalum oxyhalides such as $\text{Bi}_4\text{TaO}_8\text{X}$ ($\text{X} = \text{Cl}, \text{Br}$) have also been discovered to be active visible-light-responsive

photocatalysts.¹⁹⁷ Similarly, this photocatalyst can function as an OER catalyst in a Z-scheme system with $\text{Ru}/\text{SrTiO}_3\text{:Rh}$ as the HER catalyst to stoichiometrically evolve H_2 and O_2 under visible light. The $[\text{Fe}(\text{CN})_6]_{3-}/[\text{Fe}(\text{CN})_6]_{4-}$ shuffle can operate at lower pH levels and has a moderately negative redox potential ($E = 0.357 \text{ V}$ versus a SHE); thus, a single electron can be accepted/donated in this redox pair. A system based on ZrO_2 -modified TaON , BiVO_4 , and $[\text{Fe}(\text{CN})_6]_{3-}/[\text{Fe}(\text{CN})_6]_{4-}$ as the HEP, OEP, and redox mediator achieved a remarkable AQE of 10.3% at 420 nm in one study (Fig. 8b).¹⁹⁸ Based on the integration of Z-scheme and photoelectrochemical systems, it has been shown that the HER and OER, which are isolated in space and time, can simultaneously develop.^{199,200} In this hybrid process, a redox couple undergoes reduction, transforming water into O_2 while simultaneously converting solar energy into chemical energy. With a minimal applied bias, H_2 is generated through the electrolysis of an aqueous solution containing the reduced redox mediator. Through the use of an optimized BiVO_4 photocatalyst with a controlled quantity of surface-adsorbed Fe(III) and a redox mediator involving Fe(III)/Fe(II), impressive results were achieved, with an AQE of 38% at 420 nm and a solar-to-electric conversion efficiency of 0.65%.²⁰¹ Additionally, ionic redox mediators may absorb some of the visible light that is being received by the device or can cause corrosion with certain photocatalysts. Solid-state electron mediators have been used to overcome the drawbacks of ionic ones, and it has been revealed that reduced graphene oxide (rGO) is an efficient carrier of photoexcited charges between the HEP and OEP. Considering this fact, a visible-light-driven Z-scheme WS system was constructed by combining a metal sulfide and $\text{CoO}_x/\text{BiVO}_4$ as HER and OER catalysts, on the rGO sheets (Fig. 8c).²⁰² After the system was exposed to visible light, a steady production of H_2 and O_2 at the stoichiometric ratio was observed. Z-scheme OWS has also been achieved under visible light irradiation by using PCN as the HEP, BiVO_4 as the OEP, and rGO as the electron mediator.²⁰³⁻²⁰⁶ Additionally, some conjugated polymers have been reported to enhance the OWS in association with rGO as the electron mediator respectively.²⁰⁷

5. Strategies for enhanced photocatalytic performance

The efficiency of photocatalytic-based WS processes is affected by several parameters and thus extensive efforts have been made to develop various strategies. One of the valuable strategies to enhance the energy-capturing capability is narrowing the band gap of materials in the visible spectral range.^{60,208-213} Other methodologies involve the use of organic dyes as a photosensitizer agent to boost the sensitization⁶⁰ or doping anions/cations to introduce new band levels into the semiconductor materials' band structures to enhance the light absorption capability.^{211,212} The availability of additional states *via* electron trapping or intermediate band level modification with the assistance of defects generated by oxygen (in the form of vacancies in the



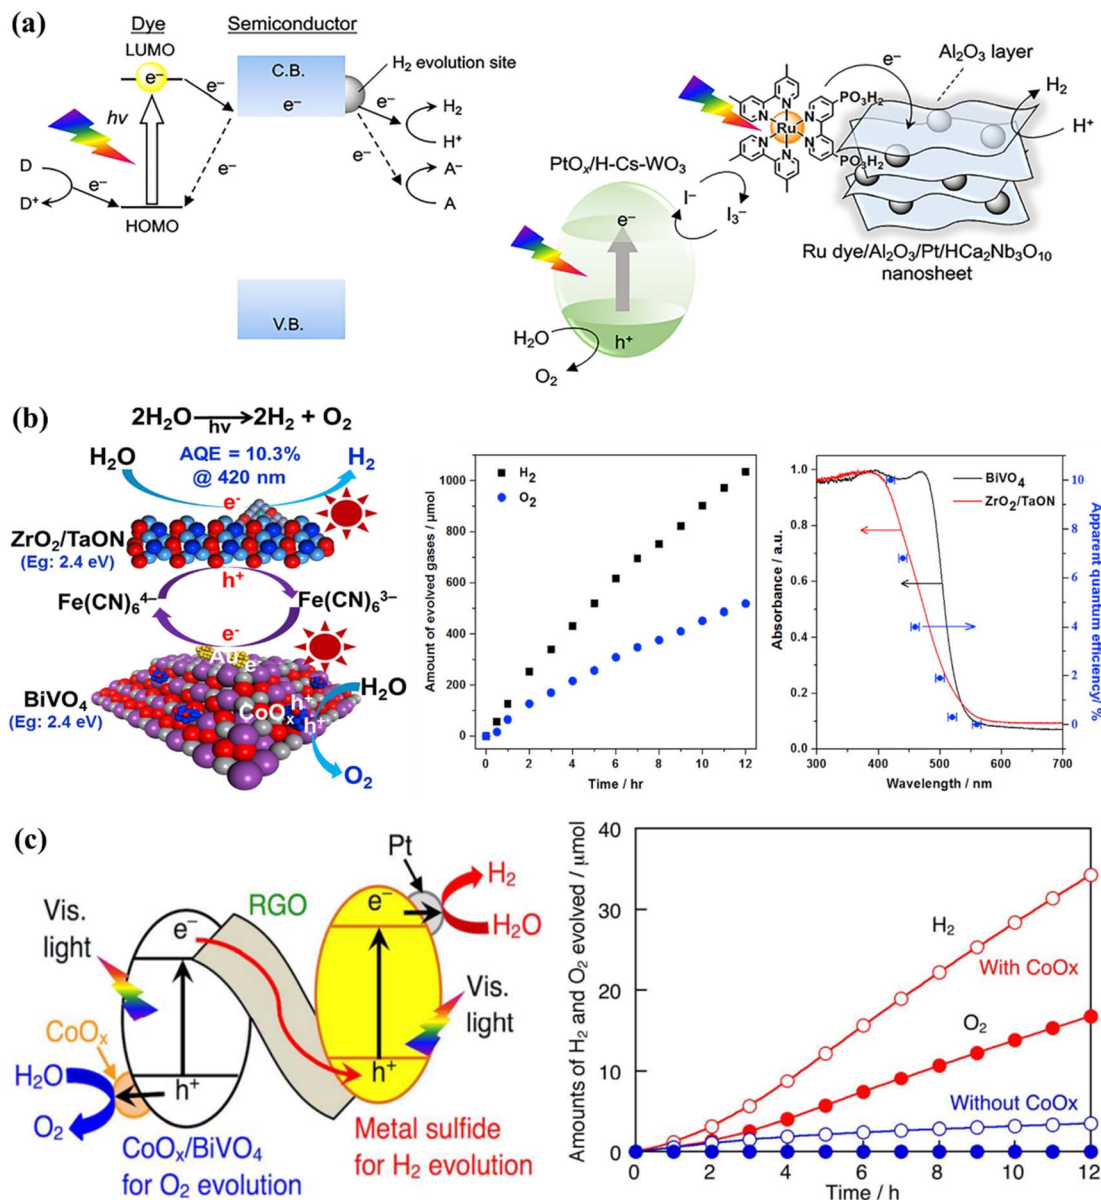


Fig. 8 (a) Typical visible-light-driven Z-scheme OWS systems using ionic redox mediators. The transfer mechanism and schematic diagrams for Z-scheme WS using $Al_2O_3/Pt/HfCa_2Nb_3O_{10}$ nanosheets sensitized with a Ru dye as the HER catalyst and $PtO_x/HfCsWO_3$ as the OER catalyst. Adapted from ref. 196. Copyright © 2020, American Chemical Society. (b) a schematic diagram of a Z-scheme system using $ZrO_2/TaON$, $BiVO_4$, and $[Fe(CN)_6]^{3-}/[Fe(CN)_6]^{4-}$ as the HER catalyst, OER catalyst, and redox mediator, respectively, and the time course of OWS under visible-light irradiation, together with the dependence curve of AQE as a function of irradiation wavelength. Adapted from ref. 198. Copyright © 2018, Elsevier, typical two-step-excitation OWS using solid-state electron mediators. (c) A diagram of a Z-scheme WS system using rGO as the solid-state electron mediator and a plot of the activity increase obtained by employing $Pt/CuGaS_2$ as the HER catalyst and $CoO_x/BiVO_4$ as the OER catalyst. Adapted from ref. 202. Copyright © 2016, American Chemical Society.

band levels) is also thought to improve the light absorption phenomena.^{214–216} The engagement of metal oxide and noble metal facilitates the surface chemical reactions by lowering the overpotentials of the OER and HER to suppress the backward reaction resulting in water formation.^{26,217–222} In addition to this method, various methodologies have been developed to promote electron and hole separation to prevent them from recombination, such as heterojunction formation, facet engineering, internal electric field generation, and so on.^{223–226} In

this section, some key strategies such as decoration with cocatalyst, dual cocatalyst deposition, polarization field engineering, temperature effect, sacrificial reagents system, morphology control, heterojunction formation, modulation of facets, and defect engineering will be investigated specifically with an emphasis on their functioning mechanism. Moreover, recently developed promising approaches based on the polarization effect to extend the exciton lifetime will also be highlighted.



5.1. Defect engineering

Surface defects that generate vacancies in semiconductor materials are recognized as an efficient way of tailoring their chemical and physical properties such as surface adsorption properties, charge separation, charge density, *etc.*^{227–230} One of the most promising strategies is vacancy-based modification. In this context, there has been advancement in the study of oxygen vacancies (Vo) present in TiO₂. The low density of Vo that naturally exists in most metal oxides can be improved through ion doping,^{231,232} plasma surface treatment,²³³ chemical reduction of NaBH₄,^{234,235} thermal treatment in an environment containing NH₃ gas,^{231,236} and exfoliation to fabricate 2D materials.²³⁷ Asahi *et al.*²⁰⁸ first proposed a strategy based on anion-doped TiO₂ for improved light absorption. Consequently, several studies were devoted to this approach by using UV-vis

spectroscopy showing that N-doped TiO₂ absorption extends to 500 nm. X-ray photoelectron spectroscopy (XPS) confirmed the characteristics of N species, with peaks emerging at 396 eV and 400 eV, respectively, associated with the substitutional and interstitial N species.^{208,231,236} Mao *et al.*²⁰⁹ explored hydrogen pre-treatment in their pioneering work, where TiO₂ was sequentially treated for five days under a hydrogen atmosphere at a temperature of 200 °C and a pressure of 20 bar. The results were promising, and black TiO₂ showed enhanced light absorption along with the photocatalytic HER. Black titania was examined using Raman spectroscopy, indicating that the hydrogenation process introduces defects responsible for activating zone-edges.²⁰⁹ Chang *et al.*²³⁸ effectively synthesized Al³⁺-loaded SrTiO₃ for the OWS performance using the PC technique. The implied materials were analyzed with multiple scientific methods and protocols in comparison to the usual



Fig. 9 (a) Diagrammatic representation of the defective pathway and carrier transport in the 2% and 1% Al-STO catalysts for milling. (b) Evaluation for durability of 2% Al-STO activated with Co (0.05 wt%), Cr (0.05 wt%), and Rh (0.1% wt%) after powder washing. Adapted from ref. 238. Copyright © 2022, Elsevier, (c and d) TEM illustration and photocatalytic performance of pristine and modified CdSe tetrapods. Adapted from ref. 246. Copyright © 2017, American Chemical Society, (e–g) HR-TEM image and photocatalytic performance of amorphous cobalt phosphide cocatalyst modified cadmium sulfide. Adapted from ref. 254. Copyright © 2016, Royal Society of Chemistry.



solid-phase milling process. The inductively coupled plasma (ICP) research shows that the Al^{3+} integration rate of the PC technique was greater compared to that of solid-phase milling. The impact of a high degree of Al^{3+} injection consistency on the chemical and physical properties and photocatalytic properties of the generated catalysts was thoroughly investigated. The photocatalytic efficiency and function of the Al^{3+} -loaded SrTiO_3 catalysts generated by the PC technique were explored depending on the assessment (Fig. 9a and b). However, recent research found that the maintenance ability of surface defects becomes fragile during the catalytic process, especially under high-temperature conditions due to their tendency to regenerate with H_2O or O_2 . In contrast, bulk defects hold their capacity for improved light absorption; still, surface defects are unable to retain their maintenance, leading to poor performance and the suppression of active catalytic sites, which may affect the photocatalytic performance. This also explains that the visible light absorption phenomenon cannot necessarily be linked with enhanced photocatalytic-based WS or AQE.²³¹

5.2. Decoration with cocatalysts

The use of cocatalysts in PWS garnered increased interest and has been focused extensively. Cocatalysts have been found to aid in charge separation and reduce recombination by promoting the extraction of exciting electrons from manipulating holes, depending on their nature. Photocatalytic-based WS and the HER based on photo-reduction of protons are considered facile processes, but the OER from OH^- involves a fundamental step that requires four electrons.^{163,239} Cocatalysts can promote O_2/H_2 surface evolution by reducing the activation energy. Metals such as Pt, Pd, Ru, Au, Rh, and Ni are commonly used for H_2 evolution, while metal oxides such as Ir, Mn, Co, and Ru are accepted as cocatalysts for the OER.²⁴⁰ Pt is widely used as an H_2 evolution cocatalyst, and recent progress has been reported in this regard. However, using cocatalysts for the HER can trigger the reverse reaction, leading to water formation. Bimetallic cocatalysts have been introduced to overcome this issue and promote the forward reaction. The Domen group reported synthesizing a core-shell structure of $\text{Rh}/\text{Cr}_2\text{O}_3$ using selective photoreduction, where the Cr_2O_3 catalyst prevented oxygen access to the metal surface, reducing the possibility of evolved O_2 . A recent study discovered that Au nanoparticle insertion by photoreduction had a substantial influence on N-doped TiO_2 , resulting in an elevated H_2 evolution rate of up to 90%.²³¹ The Domen group reported the synthesizing of a core-shell structure of $\text{Rh}/\text{Cr}_2\text{O}_3$ using selective photoreduction. In their study, the catalyst Cr_2O_3 species as a barrier prevented oxygen access to the metal surface, reducing the possibility of evolved O_2 .^{217,241} The core-shell structure of $\text{Rh}/\text{Cr}_2\text{O}_3$ and the presence of Rh and Cr_2O_3 in the core and shell were confirmed by TEM, XPS, and EXAFS analysis respectively. When GaN: ZnO was loaded onto $\text{Rh}/\text{Cr}_2\text{O}_3$, the inhibition of the backward reaction resulted in enhanced WS efficiency. A similar performance was also seen for the metal cores of Pt and Ir.²¹⁷ Despite the greater SA and shorter range of charge transfer to the reaction liquid, smaller-size cocatalyst

particles are commonly selected in photocatalysis.^{151,242,243} However, smaller-size cocatalysts have the disadvantage of poor visible light, which can decrease their shielding effect.²⁴⁴ Single-atom-based cocatalysts have been focused on due to their small size.^{245,246} However, some studies have reported that the smallest cocatalysts are not always favorable for catalytic efficiency, indicating another drawback of such cocatalysts.^{247,248} Similarly, the TEM morphology and the conflictive effects of co-catalysts on pristine and modified CdSe tetrapods regarding the charge transfer efficiency have been depicted in Fig. 9c and d.²⁴⁶ Smaller sizes accelerate the electron moment to access the solution of cocatalysts quickly and are effective in suppressing the phenomenon of electron acceptance from host catalysts to cocatalysts. Another perception of the size dependence is based on the various types of photocatalyst hosts, because each type holds different surface catalysis and charge transfer characteristics.^{249,250} Despite size, another affecting component is the shape/structure of cocatalysts, which can be critical in determining overall activity.²⁵¹ Variation in the structure of each entity offers distinctive exposed facets, leading to differences in absorption energy for WS and active sites. To enable efficient cocatalysts, another important morphology is the hollow structure, which offers efficient charge transport and mass transfer as a result of its unique structure.²⁵² Cocatalysts with fewer defects in their crystalline structure have shown good performance. Still, recent studies have highlighted the importance of amorphous cocatalysts.²⁵³ These have exhibited excellent charge transfer capability and photocatalytic performance by developing a core-shell structure with amorphous cobalt cocatalysts (CoP_x) integrated with CdS nanorods (Fig. 9e-g).²⁵⁴ Amorphous cocatalysts can trap electrons, facilitate proton adsorption, enhance kinetic charge transfer capability and have shown a high AQE of up to 97.42%.²⁵⁵

5.3. Photocatalysis at elevated temperatures

In the past decade, research on PWS has predominantly focused on room temperature conditions. However, it has been shown that raising the temperature can enhance the thermodynamic and kinetic performance of endothermic reactions. The thermolysis process, requiring very high temperatures (around 1000 °C), is impractical for real-world applications.⁶⁵ Nevertheless, the use of elevated temperatures for efficient photocatalysis offers a new approach to harnessing solar energy, taking advantage of the fact that solar sources can also supply heat. Additionally, nearly 50% of the solar spectrum consists of infrared radiation, which can provide the necessary heat energy through thermal radiation, therefore eliminating the need for expensive electrical devices.^{256,257} S. C. E. Tsang *et al.*²³³ describe an instantaneous PWS method that can successfully use sunlight at high temperatures, with substantially greater H_2 production rates and QEs than the Au/N-loaded TiO_2/MgO (111) nanocatalyst because of the longer excitation duration in this structure. Consequently, at 270 °C, a wide absorption spectrum appears, generating O_2 and H_2 sources in a 1 : 2 molar proportion with an H_2 generation activity of about 11 000 mol $\text{g}^{-1} \text{h}^{-1}$. The Q.E. spectrum is very remarkable and extends from 81.8%



at 437 nm to 3.2% at 1000 nm (Fig. 10a–c). B. Han and Y. Hu²⁵⁸ proposed a photocatalytic HER system based on the temperature-induced mechanism which achieves an AQE of up to 65.7% (with methanol as a sacrificial reagent) at a temperature of 280 °C under visible light. The increase in temperature supplies thermal energy to the reactants, as well as an increase in kinetic driving force, which is responsible for the increase in AQE and the HER. B. Tian *et al.*²⁵⁹ utilized black phosphorous nanosheets in a PWS process carried out at high temperatures. Their proposed system demonstrated a nine-fold increase in PWS at a temperature of 353 K compared to room temperature, resulting in an increase in QEs up to 42.55%. It should be noted that sacrificial reagents were not considered in their study.²⁵⁹ However, the absence of oxygen in their proposed system makes

it susceptible to photo-corrosion of the phosphide catalyst, which is one of the drawbacks. Water dissociation can be promoted up to 25 times compared to the dissociation carried out at room temperature and its high temperature of ~ 270 °C making it suitable for enhancing PWS kinetically.⁴¹ Despite the increase in performance, it is not frequently reported. With motivation from previous research to encourage WS caused by increasing temperature, an exceptional AQE of up to 81.8% (at 437 nm and 270C) for a TiO₂-based photocatalyst was recently reported. It is worth mentioning that an AQE of 3.2% was also testified at 1000 nm, obviously indicating a theoretical threshold for PWS.²³¹ Charge carriers approaching the surface of a photocatalyst are also considered crucial compared to those that settled down in the bulk region.



Fig. 10 PWS response function testing. (a) Photocatalytic activity of N-P25-620 and Au/N-P25-620 with MgO (111) at various temperatures. (b) Effective stoichiometric WS with no sacrificial agent over Au/N-P25-620 with and without MgO (111) at an identical speed for 50 h. (c) QE of Au/N-P25-620 in conjunction with and without MgO (111) assuming incoming wavelengths, this is an open access article distributed under the terms of the Creative Commons CC BY license.²³³ (d) A schematic illustration of Pt along with the separation and migration of electrons and holes in the bulk of pure and C-doped Bi₃O₄Cl. Adapted from ref. 266. Copyright © 2016, John Wiley and Sons.



5.4. Polarization field engineering at elevated temperature

After the light absorption, the charge carriers migrate to the photocatalyst surface.²⁶⁰ Photoexcitation generates electrons and holes in femtoseconds but charge separation and migration typically take much longer respectively. The photoexcited electrons/holes prefer to recombine and release energy in heat instead of traveling to the surface that reacts with chemical species, and therefore this process takes approximately 10^{-12} s. However, the transfer of charge to the chemical species at the interface is a relatively slow process that occurs in the range of microseconds to picoseconds, showing that electrons and holes prefer recombination instead of migration to the surface.^{261,262} This implies that only a small number of photoinduced electrons/holes emitted by photocatalysts that improve light absorption reach the photocatalyst surface, resulting in low quantum efficiencies. The photoexcited electrons/holes have enough lifetime to capture H^+ and OH^- ions produced from water molecules to boost photocatalysis.^{231,263} Polarization enhancement is required to promote separation of photo-generated electrons and holes inside the same particle to reduce the recombination of electrons and holes on the surface. An increase in polarization has been demonstrated recently by introducing an electric field and proving a solid approach to enhance separation on the surface and in bulk.^{39,264} L. Zhang group²²³ proposed that carbon incorporation could be used to apply the internal electric field to Bi_3O_4Cl , which results in bulk charge separation of up to 80%. The excitation lifetime of this C-doped Bi_3O_4Cl was extended from 500 ps to 4000 ps associated with the introduction of a strong electric field. In addition, this group reported another Janus $Cl_2-Bi_{12}O_{17}-MoS_2$ bilayer junction photocatalyst capable of producing a strong internal electric field suitable for the HER. Using ascorbic acid as a hole collector, this material reported a carrier lifetime of 3446 ns and an HER of $33 \text{ mmol g}^{-1} \text{ h}^{-1}$.²⁶⁵ To enhance the local electric field (LEF) for improved charge separation, a polar-faceted material was recently developed by engaging faceted MgO (111). The availability of both positive and negative terminated surfaces generates a strong LEF, such as the nanocrystal of polar MgO (111), which has positive (Mg^{2+}) negative (O^{2-}) terminated surfaces. To confirm the surface polarity, TEM and solid-state NMR were used as characterization methods.²⁶⁴ TRPL testing conducted after mixing with N-doped TiO_2 indicated MgO (111) participation in extending N-doped TiO_2 excitation lifetime from 2.56 ns to 5.76 ns. The inclusion of MgO (111) also increased QEs, such as 3.2% at 1000 and 81.8 at 437 nm. Polar faceted MgO (111) has been associated with increasing excitation lifetimes and therefore PWS activities, thereby dominating the oxygen vacancy effect mechanism. Investigations were further expanded to probe the LEF effects of other polar-faceted oxides (PFOs) with different morphologies and sizes of N-doped TiO_2 . Smaller size particles were found to be more effective in enhancing LEF-based activities.²⁶⁵⁻²⁶⁷ On the polar surfaces, a non-zero electric dipole moment is achieved by growing each repeated unit perpendicularly on the surface of the first one. Therefore, due to their different local environments, their surface properties differ from those of their non-polar

counterparts (Fig. 10d).²⁶⁶ At the outermost plane of the high-energy polar surface, the compensation of electric charges and charge transfer leads to the ability to cancel the electrical polarity.²⁶⁵ However, some oxides are rigid and leave significant polarity on the polar surfaces, which is considered an excellent sign to enhance the local electrical polarization.

5.5. Sacrificial reagent systems for water splitting

Compared to the OWS process, it is more practical to examine the two semi-reactions independently by incorporating sacrificial reagents. Although these reactions do not represent actual OWS, they can aid in comprehending the mechanism behind it and offer practical guidance for the assembly of photocatalysts that exhibit efficient activity in photocatalytic overall water splitting (POWS). Researchers have shown greater interest in the HER, rather than the OER, in the context of solar energy conversion and utilization, because H_2 serves as a vital energy source for our future needs. Consequently, significant emphasis has been placed on developing sacrificial reagent systems for the efficient production of H_2 . The fundamental processes involved in the production of H_2 through the use of sacrificial reagents, namely CH_3OH , triethylamine, and Na_2S/Na_2SO_3 , which act as electron donors (referred to as D/D⁺).²⁸ These sacrificial reagents consume the holes generated during the photochemical reaction and allow the electrons to react with H_2O , leading to the photocatalytic evolution of H_2 . A. Abdel-Wahab *et al.*²⁶⁸ conducted a comprehensive scientific study on WS performance, employing three potential catalysts, titania (TiO_2-P_{25}), graphitic carbon nitride ($g-C_3N_4$), and cadmium sulfide (CdS). The study rigorously tested these catalysts using various sacrificial reagents, including commonly used ones such as sodium sulfide, ethylene glycol, sodium sulfite, lactic acid, glucose, ethanol, methanol, isopropanol, glucose, sodium sulfite/sodium sulfite combination, and triethanolamine, on TiO_2-P_{25} , $g-C_3N_4$, and CdS. In a complete immersion model photo-reactor, H_2 synthesis studies were performed under approximated solar light illumination, and notably no precious metal co-catalyst was employed in any of the experiments. In addition, photolysis studies were carried out to investigate H_2 formation in the absence of a catalyst. The study investigated various aspects, including chemical reactions, the pH of the reactivity medium—high heat, the hydroxyl groups, alpha hydrogen, and the length of the carbon chains of sacrificial reagents. The detailed finding revealed that, among the sacrificial agents investigated, glucose and glycerol are the best sacrificial reagents for oxide catalysts, as illustrated in Fig. 11a–d. The oxidation potential of the sacrificial reagent surpasses that of H_2O , resulting in an increased driving force for the oxidation half-reaction. As a result, the consumption of photogenerated holes speeds up, leading to a decrease in the loss of photogenerated electrons through recombination.^{90,177,216,269-272} Moreover, employing this approach effectively hinders the photo-corrosion of photocatalysts, particularly metal sulfides. For instance, it has been observed that CdS is susceptible to instability in the process of photocatalytic H_2 evolution, as the S_2 -ions in CdS are





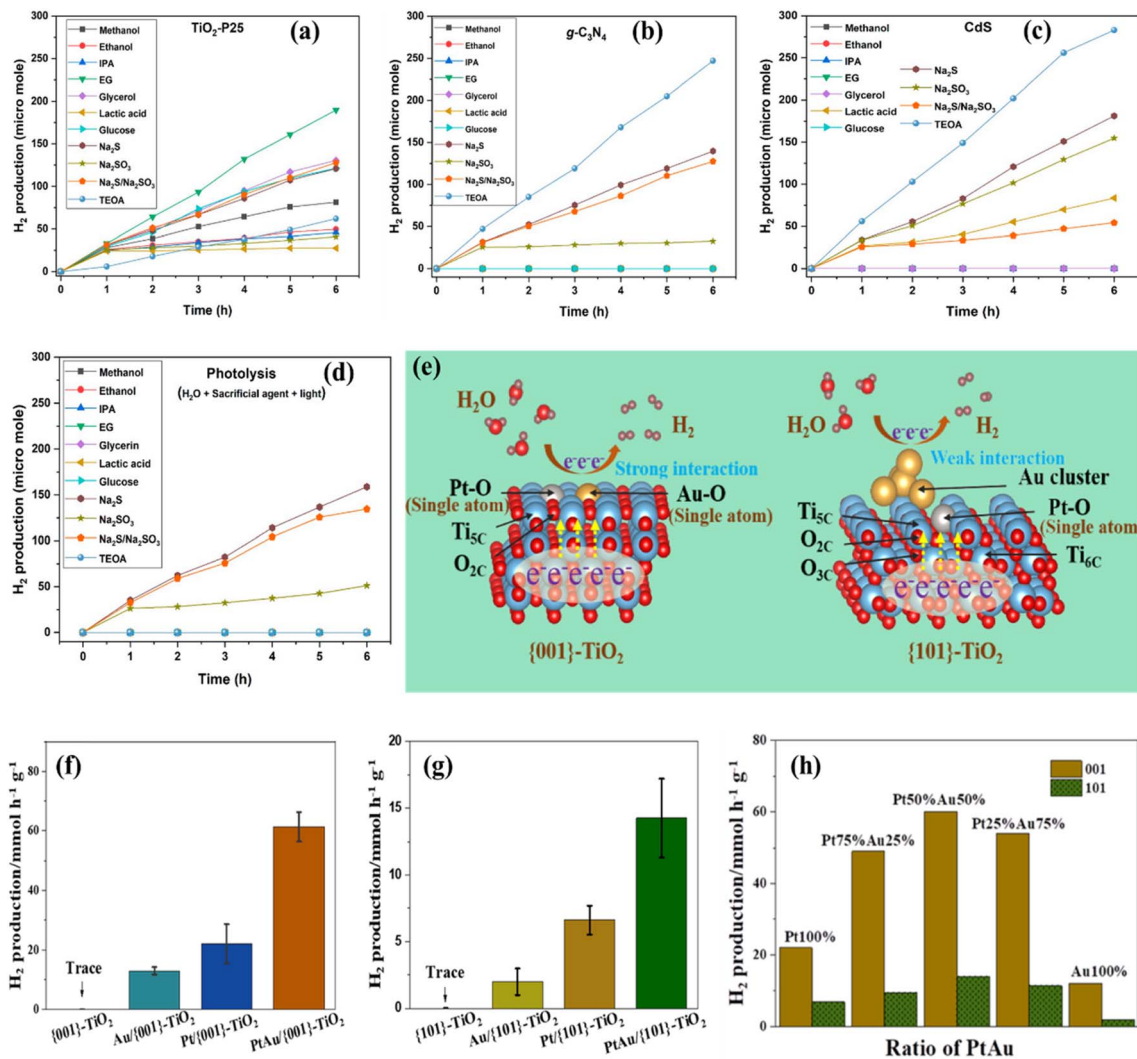


Fig. 11 (a–d) PWS using different photocatalysts having multiple sacrificial reagents.²⁶⁸ (e–h) {001}- and {101}-faceted TiO₂ and PWS performance of Pt–Au/{001}-TiO₂ under light illumination. Adapted from ref. 279. Copyright © 2021, American Chemical Society.

susceptible to self-oxidation by the photoinduced holes present in the VB of CdS as shown in eqn (6).^{273,274} However, by utilizing sacrificial electron donors to consume the photo-generated holes, the occurrence of photo corrosion can be effectively restricted.



During the conversion process, when methanol is employed as an electron donor, H₂ is generated from water, as described in eqn (7).^{275–277} Conversely, Guzman and his team²⁷⁶ observed a low rate of H₂ production from CH₃OH solutions when using a Cu/S–TiO₂ catalyst under UV illumination. This observation suggests that, in the presence of a high concentration of water, the reaction between the hole and CH₃OH does not take place significantly. On the other hand, the process of oxygen

evolution is considerably more challenging from both a thermodynamic and kinetic perspective.

5.6. Dual cocatalyst systems for water splitting

An effective method for achieving PWOS involves the simultaneous addition of dual cocatalysts, which encompass both reduction and oxidation cocatalysts, onto the light-absorbing semiconductor material. This approach proves particularly successful when employed with semiconductors that possess suitable band gaps and energy levels for facilitating the OWS process. The introduction of dual cocatalysts has demonstrated a substantial enhancement in the efficiency of PWOS. For instance, Li and his research team²⁷⁸ observed that combining Zn₂GeO₄ with noble metals (such as Pt, Pd, Rh, and Au) and metal oxides (such as RuO₂ and IrO₂) produces a remarkable synergistic effect, significantly boosting the photocatalytic activity during the OWS process. This phenomenon becomes evident when considering the Pt–RuO₂/Zn₂GeO₄ catalyst, which



exhibits 2.2 times the photocatalytic activity compared to Pt/Zn₂GeO₄ and 3.3 times the photocatalytic activity when compared to RuO₂/Zn₂GeO₄. These data strongly suggest that Pt and RuO₂ play dual roles in enhancing the POWS. They not only serve as electron and hole traps, facilitating the separation of electron-hole pairs, but they also serve as catalytic sites for the generation of H₂ and O₂. The incorporation of dual cocatalysts represents a cutting-edge development aimed at significantly enhancing the efficiency of PWOS. Wei *et al.*²⁷⁹ provided a novel technique for crystalline facet-induced coordinating tuning of Pt-Au dimer co-catalysts. Researchers established that the electrical surroundings of catalysts were extremely facet-dependent by progressively distributing Pt and Au particles over TiO₂ catalysts with accessible 001 and 101 sides. Due to the elevated surface energy and unbalanced Ti⁴⁺ locations, heteronuclear Pt-Au double ions were fixed on the 001 sides of TiO₂

via PtO and AuO bonds, whereas the 101 sides remained susceptible to combining with Au ions through loosely bound Au tiny clusters. The maximal H₂ generation ratio of the dual-atom co-catalyzed materials was 61.5 mmol h⁻¹ g⁻¹, which was 3 and 5% higher than that of the single-atom equivalents of Pt/TiO₂ and Au/TiO₂ (Fig. 11e-h).

5.7. Morphology control of photocatalysts

Photocatalysts are divided into four kinds based on their dimensional morphology: first, there are 0D photocatalysts (quantum dots); second, there are 1D nanowires, nanotubes, and nanorods. Third, there is the 2D grouping of nanosheets, followed by the 3D classification of nanoclusters and nanoporous materials.²⁸⁰ In 1995, researchers for the first time confirmed the influence of morphology on catalytic activity of

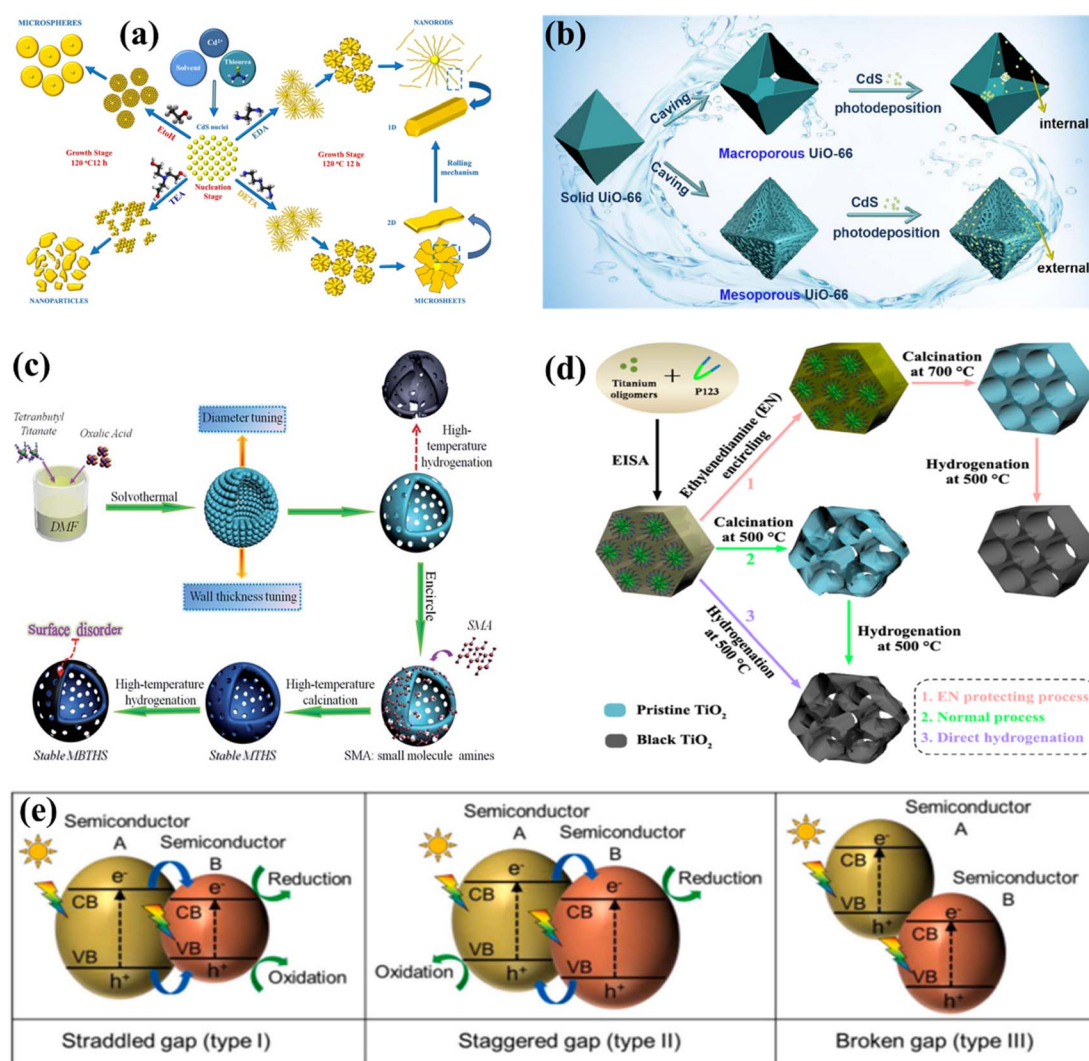


Fig. 12 Morphology control of photocatalysts: (a) schematic of CdS structures with various morphologies (120 °C and 12 h). Adapted from ref. 283. Copyright © 2017, Elsevier, (b) scheme illustrating the fabrication of distinct macro- and meso-porous CDS/UiO-66. Adapted from ref. 289. Copyright © 2021, Elsevier, (c) schematic illustration of the mesoporous TiO₂ nanomaterials. Adapted from ref. 287, Copyright © 2016, Royal Society of Chemistry, and (d) schematic illustration of the ordered mesoporous TiO₂ nanomaterials. Adapted from ref. 288 Copyright © 2014, American Chemical Society, (e) heterojunctions of liquid phase Z-type, all-solid-state Z-type, and direct Z-type heterojunctions. Adapted from ref. 302, Copyright © 2023, Elsevier.



semiconductors. They found that porous TiO_2 displayed significantly higher AQE in comparison to bulk TiO_2 . Since this discovery, scientists have focused on controlling and optimizing the morphology of the photocatalyst to enhance its SA, improve optical absorption, minimize the distance for carrier transport, and increase the exposure of the reaction site.^{281,282} Modifications in the structure of the catalysts can greatly influence their photocatalytic activity. This has been found in the case of CdS crystal materials, where changes in structural order from nanorods to nanosheets, to irregular nanoparticles, and microspheres show a decline in HER efficiency, as depicted in Fig. 12a.²⁸³ This decline is attributed to the inclusion of small CdS nanocrystals within the nanorods and nanosheets, leading to a noticeable quantum confinement effect. In the case of conjugated porous polymers having 2D nanosheet morphology, they have shown a 20 times greater HER than their bulk counterparts.²⁸⁴ Similarly, J. Kosco²⁸⁵ reported that a significant increase in H_2 production has been found when organic nanoparticles are synthesized from PTB7-Th (donor polymer) and EH-IDTBR (non-fullerene acceptor) and then put through a structural transformation process including intermixed donor/acceptor blends. These structural changes often lead to increased exposure of the reaction sites and shorter distances for carrier migration. Furthermore, doping oxygen into $g\text{-C}_3\text{N}_4$ nanotubes has proven to be remarkably effective in enhancing HER activity, surpassing the performance of most $g\text{-C}_3\text{N}_4$ nanotubes.²⁸⁶ Similarly, Hu *et al.*²⁸⁷ and Zhou *et al.*²⁸⁸ reported that mesoporous configurations and hollow nanotubes or spheres play a crucial role in enhancing light absorption by enabling multiple diffuse reflections during photocatalytic reactions (Fig. 12c and d). Metal-organic frameworks (MOFs) have become widely employed as substrates for advanced catalysts, as depicted in Fig. 12b. It has been found that the pore size of MOFs plays a crucial role in determining the efficiency of photocatalysis.²⁸⁹ Covalent organic frameworks (COFs) based on 3D morphologies have also been proven advantageous when used as a reference for enhancing the composite catalyst structure. Moreover, incorporating 0D quantum dots into organic frameworks is a common practice for improving the absorption of irradiation. The arrangement of Au nanodots within thiol-functionalized UiO66 MOF can influence the migration of charge carriers.²⁹⁰ Finally, a range of 3D structural configurations, such as mesoporous nanospheres, nano-flowers,²⁹¹ and micro-flowers,^{292,293} have been designed to attain superior photocatalytic performance.

5.8. Construction of heterojunctions

Semiconductor photocatalytic heterojunctions hold the capability of suppressing carrier recombination and, thus, can also boost the separation efficiency of carriers. Heterojunction construction is achieved by embedding different semiconductors to connect their interfaces with face- or point-connections. Such an interface structure provides ease for the transfer and separation of carriers, which is considered vital for enhanced photocatalytic performance. Typically, heterojunctions are categorized based on energy band alignment

types, such as straddled, staggered, and broken gaps. Taking into account the case of a straddled gap structure, the occurrence of one semiconductor band is located within the domain of the other. On the other hand, band overlapping does not exist in the broken structure. Only staggering energy band gaps among them achieve the separation of holes from electrons under photoexcitation conditions.^{294,295} The thermodynamic and kinetic studies have highlighted one of the basic problems existing in the straddled band gap among the two semiconductors, which is the accumulation of carriers at the low position of the CB and the high position in the case of the VB. This gathering of charges leads to a reduction in redox capability, which governs the photocatalytic reaction to the inhibition. Apart from this, the electrostatic repulsive force among the same charges suppresses the migration of carriers. Eventually, these phenomena evolve into challenging problems from the perspective of dynamics and thermodynamics. The Z-type heterojunctions offer efficient carrier separation without compromising the redox capability, as shown in the schematic illustration in Fig. 12e. These are further categorized into three types, Z-type with a liquid-phase, Z-type with an all-solid-state, and construction with a direct Z-type heterojunction. Nevertheless, the utilization of a redox electron-facilitator pair comes with some challenges. One of these is that the working ability of the facilitator-pair is only limited to the selected solution requiring certain pH values. More than that, interference between the optical absorption of semiconductors and the facilitator-pair restricts the extension in the application scale of Z-type heterojunctions with the liquid phase. In discrepancy, these problems are lessened in Z-type with direct heterojunctions^{296,297} and Z-type with all-solid-state heterojunctions,^{298,299} placing them in the list of suitable candidates for the industrial application. A photocatalytic heterostructure employing the S-scheme was confirmed to be a novel heterostructure.³⁰⁰ S-scheme heterojunctions have an advantage over conventional heterojunctions due to their unique charge transfer mechanism, which also allows for the preservation of valuable carriers, reorganization of photocarriers through the use of an internally generated electric field, bending of a band, and electrostatic interaction.³⁰¹ In particular, when a photocatalyst based on a reduced semiconductor comes into contact with a photocatalyst based on an oxidized semiconductor, electrons travel from the reduced semiconductor to the oxidized semiconductor, generating an electric field that bends the bands in the reduced- and oxidized-semiconductors and aligns the fermi levels at the same level.

5.9. Modulation of facets

Another approach to enhance the photocatalytic activity involves facet modulation. It is widely acknowledged that TiO_2 nanocrystals with a significant presence of high surface energy facets, such as {001}, {010}, and {111}, can provide a more significant number of active photocatalytic sites.³⁰³⁻³⁰⁵ However, it's important to note that these facets inherently possess thermodynamic instability and tend to diminish rapidly during the crystal formation process to minimize the overall crystal



energy. As a result, the most stable $\{101\}$ aspects have the largest effect on anatase TiO_2 .^{231,303} Chang *et al.*³⁰⁶ used DFT in conjunction with extensive description to clarify the cause of the K-modulated facet and defects in SrTiO_3 nanoparticles, which in turn influences the POWS. Researchers discovered that non-equivalent facets were exposed as a result of the variations in binding capacity among K_2CO_3 and various aspects. Using facet technology, researchers were able to show that the K-loading mechanism involved refilling and replacement processes, with a minimal number of defects at their junction and an optimal bending extent of energy from the surface bands across facets $\{100\}$ and $\{110\}$. In further explanation, the crystalline structure of seeding and the degree of development of various crystallography facets are being identified as critical elements

influencing the ultimate form of the resulting formation of a nanostructure. Using thermodynamics to control the interface energy of various components has proven to be an effective technique to control their rate of growth. The degree of interaction between impurities and metals may modify the sequence of free energy in several aspects, resulting in varying rates of development in solution-phase production. As a result, a more gradual development speed could be advantageous to the accessibility of the relevant aspect. The significant interaction among citrate ions and the $\{111\}$ facets of Pd, promoted their contact, favoring the production of Pd octahedra. According to structural analysis, the geometry of K-loaded SrTiO_3 differs substantially from that of pure STO, displaying 110 facets at the reduced edges and 111 facets at the junction. In a similar


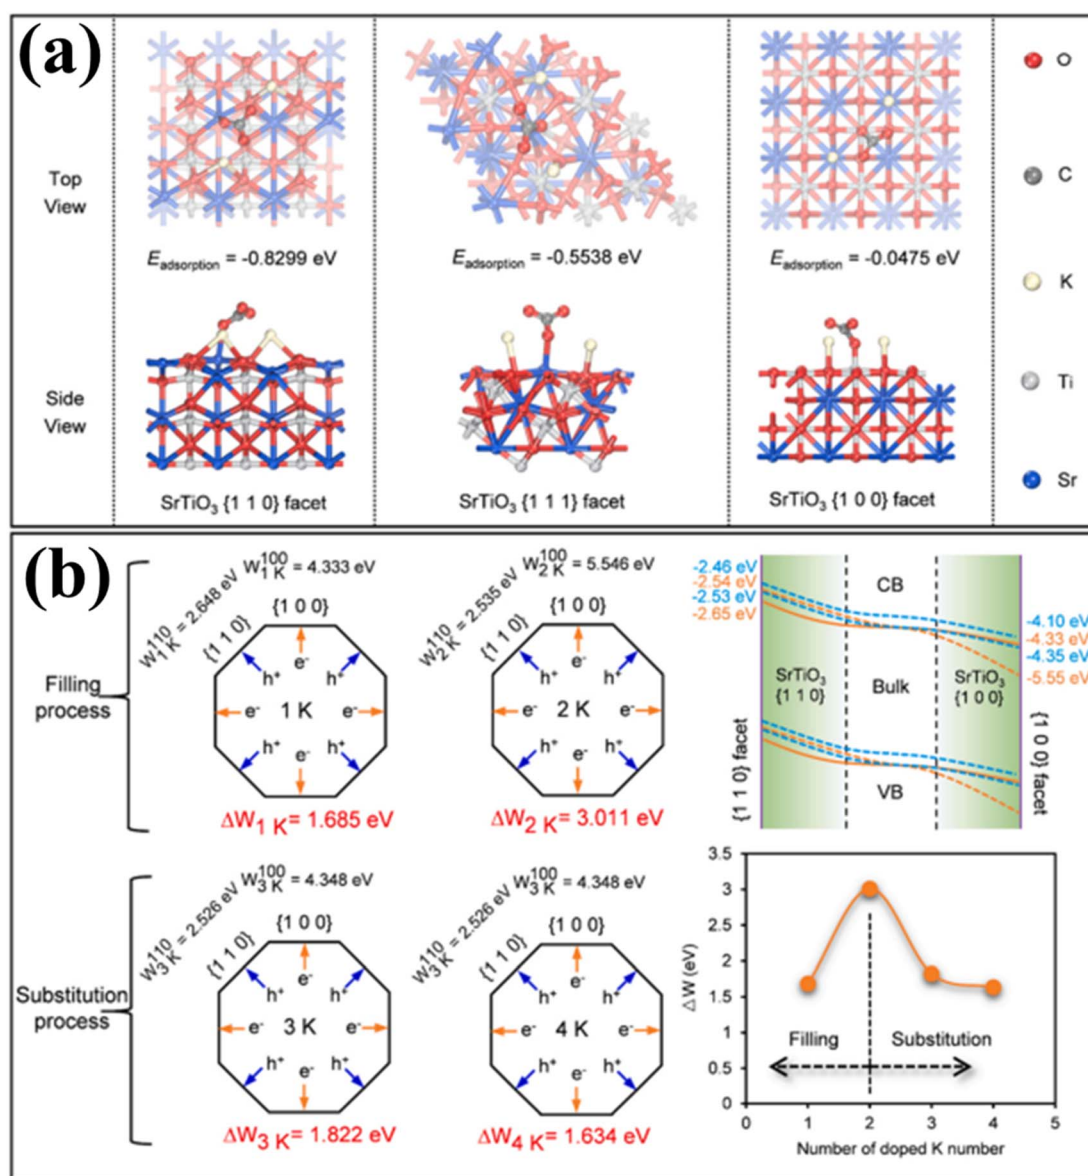


Fig. 13 (a) The adsorption energies of various SrTiO_3 crystalline facets to K_2CO_3 ; (b) work function values of $\{110\}$ and $\{100\}$ facets for K loaded SrTiO_3 at the work function variations, and conceptual band illustrations throughout the boundaries among the $\{110\}$ and $\{100\}$ facets of an exposed single K loaded SrTiO_3 catalyst. Adapted from ref. 306. Copyright © 2022, Elsevier.



manner it was inferred that they were mostly determined by the bonding affinities of K_2CO_3 to various facets of K loaded $SrTiO_3$. The adsorption energy values of the $\{100\}$, $\{110\}$, and $\{111\}$ facets to K_2CO_3 were subsequently calculated using DFT to establish the bonding capacity, as shown in Fig. 13a. The total adsorption values were 0.8299 eV, 0.5538 eV, and 0.0475 eV, correlating to the $\{110\}$, $\{111\}$, and $\{100\}$ facets, correspondingly. This finding revealed that K_2CO_3 was simpler to adsorb onto $\{110\}$ facets, indicating that its bonding intensity was higher. Furthermore, Fig. 13b shows the basic band schematics at the boundary connecting the $\{100\}$ and $\{110\}$ facets of an individual K loaded $SrTiO_3$ particle. In this case, the computed Fermi energy matched the highest point of the CB under realistic conditions. Similarly, Liu *et al.*³⁰⁷ conducted a comparative analysis of TiO_2 nanocrystals that featured $\{101\}$, $\{100\}$, and $\{001\}$ facets in terms of their ability to generate H_2 . Such experiments were performed using a methanol solution with a concentration of 20% V/V under the irradiation of a 300 W Hg lamp with a wavelength of approximately 365 nm. Their findings demonstrated that the $\{100\}$ and $\{001\}$ facets displayed significantly higher rates of H_2 evolution in comparison to the $\{101\}$ equilibrium facet.

6. Materials for photocatalysis

6.1. Description and material design

As mentioned earlier, an ideal photocatalyst should have a band gap of at least 1.23 eV and resist photo corrosion. To regulate photogenerated electrons and holes, excellent crystallinity and small particle size are necessary. The WS level has employed a variety of metal oxides, sulfides, nitrides, and phosphates. The catalysts for PWS can be developed utilizing Group I and II metals, as well as lanthanides. A range of semiconductor band structures suitable for WS are displayed in Fig. 14a. Co-catalysts such as Pt, RuO_2 , Au, and NiO can be used to improve the HER, while transition metal cations such as V^{5+} , Ni^{2+} , and Cr^{3+} can increase photocatalytic efficiency and sensitivity to visible light.

6.2. Titanium dioxide (TiO_2)

Fujishima and Honda²⁹ demonstrated that TiO_2 is an effective photoanode for POWS driven by UV light. TiO_2 has received a lot of attention as a photocatalyst because of its chemical stability, low cost, and eco-friendliness, as well as its adjustable energy band gap.^{308,309} Fig. 14b shows the band gap of TiO_2 . However, TiO_2 has two significant drawbacks: it suffers from rapid recombination of charge carriers, which consumes energy, and it cannot use visible light.³¹⁰ TiO_2 only requires UV light to achieve its 3.0–3.2 eV band gap, which represents less than 5% of the solar spectrum.³¹¹ These processes are examined in extensive detail. Similarly, modifications including doping, heterojunction formation with metals or other semiconductors, and structural modification are needed to allow visible light harvesting without the recombination of photogenerated electron–hole pairs. TiO_2 can be doped with various elements to minimize charge recombination and modify its optical properties.³¹² Metals and non-metallic elements such as F, B, S, C,

and N, have been extensively studied for this purpose.^{313,314} Luo and coworkers³¹⁵ synthesized Br and Cl-doped TiO_2 using titanium chloride and hydrobromic acid as a source. The band gap of Br and Cl-doped TiO_2 was reduced due to the presence of non-metal dopants, resulting in better solar light-induced WS. According to Faria *et al.*³¹⁶ doping TiO_2 with carbon-based compounds also increases its photocatalytic activity to visible light. Three potential pathways exist for the synergistic action of carbon on TiO_2 ; however they are still not completely explored. In order to inhibit recombination and constrain the aggregation of TiO_2 nanoparticles, carbon can function as an electron sink or a photosensitizer.³¹⁷ Electrons may be able to penetrate the CB of TiO_2 by the second process, which involves carbon acting as a photosensitizer. Additionally, carbon can prevent TiO_2 nanoparticles from accumulating.³¹⁸ It is also possible to develop a new optical absorption edge and decrease the energy barrier through the addition of metallic dopants into the TiO_2 band gap.^{319,320} For instance, Fe-doped TiO_2 exhibits improved PWS activity. The heterojunctions between semiconductors can limit charge recombination by generating electron–hole pairs with a long lifetime.³¹⁴ Proper band alignment promotes charge transfer across semiconductors. Fig. 14c depicts the band alignment of doped TiO_2 semiconductors. Resasco *et al.*³²¹ suggested a $TiO_2/BiVO_4$ host-guest photoanode system. The system exhibited better performances than $BiVO_4$ or TiO_2 alone, owing to the high electron affinity of the photo-anode heterojunction (Fig. 14d). TiO_2 can efficiently oxidize or reduce water using a sacrificial agent. In the presence of TiO_2 , lower oxidation potential reagents such as ethylene, ethanol, methanol, and glycol are commonly employed to reduce electron–hole pair recombination.³²² Charge separation and reduced recombination occur when the band gaps of two semiconductors are matched. In this scenario, one semiconductor possesses a higher valence band (VB) energy compared to the other, while its conduction band (CB) energy is lower.³²³ In metal semiconductors, co-catalysts such as Au, Pt, Pd, and Ru function as electron sinks. Au has a high affinity for photogenerated electrons, low-side reaction activity, and surface plasmon resonance.^{324,325} Ko *et al.*³²⁶ employed a Wulff-construction technique to synthesize a range of anatase and rutile TiO_2 nanomaterials (ranging in size). The HOMO and LUMO energies of TiO_2 materials were determined using size-dependent energy balance scaling. The results were subsequently displayed as an estimate of $n^{-1.35/3}$, where n is the total amount of TiO_2 units, as illustrated in Fig. 14e and f. Wu *et al.*³²⁷ investigated anisotropic TiO_2 growth on Au nanorods and discovered an electron surface plasmon resonance between TiO_2 and Au. Optimizing the structure could boost the HER under visible light.

6.3. Metal oxides

Owing to the aqueous solution stability and inexpensive cost, additional common metal oxides such as Ga_2O_3 , Al_2O_3 , ZrO_2 , CoO , Fe_2O_3 , Cu_2O , WO_3 , ZnO , and Ta_2O_5 have also been extensively explored. However, the bulk of metal oxides have significant band gaps that prevent them from absorbing visible





Fig. 14 (a) Illustration of several semiconductor band structures for water-splitting redox potentials. Adapted from ref. 328. Copyright © 2016, Royal Society of Chemistry, (b) TiO_2 band gap diagram. Influence of doping on photocatalytic properties of the TiO_2 catalyst. Adapted from ref. 329. Copyright © 2014, Royal Society of Chemistry, (c) schematic representation of the band gap alignment of S, Fe, and V doped TiO_2 . Adapted from ref. 330. Copyright © 2015, Royal Society of Chemistry, (d) band gap alignment of the $\text{TiO}_2/\text{BiVO}_4$ heterojunction. Adapted from ref. 321. Copyright © 2016, American Chemical Society, (e and f) The calculated HOMO and LUMO energies for anatase TiO_2 nanomaterials and the rutile TiO_2 nanomaterials as a consequence of $n^{-1.35/3}$. Adapted from ref. 326. Copyright © 2017, American Chemical Society.

light. The VB and CB of metal oxide are generally O 2p and metals. As a result, materials with a high degree of ionic bonding have broad band gaps, such as ZnO (3.4 eV),³³¹ Fe_2O_3 (2.0 eV)^{332–335} and Co_3O_4 (1.3 eV).³³² Two transition metal cations with dn electronic configurations Fe^{2+} and Co^{2+} can assist in resolving this issue.³³⁶ However, these cations have low polarized driven conductance and high resistivity, implying that effective charge carrier transmission is limited.³³⁷ Ternary metal oxides such as $\text{Bi}_{20}\text{TiO}_{32}$ field,³³⁸ SnNb_2O_6 field,³³⁹ and BiVO_4 field,^{332,340} have been investigated to address these challenges and have been explored for their water redox potential due to their narrow band gap (2.4–2.5 eV) and excellent band edge alignment, making them a promising candidate (Fig. 15a). Additionally, BiVO_4 exhibits both n- and p-type semiconducting

characteristics and high photon to current conversion efficiencies (more than 40%).³⁴¹ Mishra *et al.*³⁴² reported that Fe_2O_3 photocatalysts have a band gap of 2.2 eV, which enhances photon absorption upon visible light. However, the use of Fe_2O_3 has been limited due to significant bulk recombination. Haghghat *et al.*³⁴³ explored electron transport in iron oxide photocatalysts with variable pH and potential space. Morales-Guio *et al.*³⁴⁴ synthesized an optically transparent photocatalyst for the OER process using amorphous iron–nickel oxide (FeNiO_x). Researchers obtained strong activity at a low overpotential, STH conversion efficiencies more than 1.9%, and “100% faradaic” conversion in unsupported WS with low FeNiO_x loading. WO_3 has been proposed as an ideal photoanode material due to its good valence band position, which



results in a larger onset potential for water oxidation than Fe_2O_3 .³⁴⁵ Amer *et al.*³⁴⁶ demonstrated the alteration of ZrO_2 by depositing thin ZrN coatings on ZrO_2 nanotubes to form core-shell structures for visible-light-activated photoanodes. Similarly, Moniz *et al.*⁹ observed that anodic photo-corrosion is a significant drawback of WO_3 . These low- E_g materials (Fe_2O_3 and WO_3) can be modified by coupling metal cations or generating heterojunction structures with other semiconductors.³¹⁹ G. S. Costa *et al.*³⁴⁷ described using a $\text{WO}_3/\text{Fe}_2\text{O}_3$ photoanode for water oxidation, owing to the significant band gap alignment between WO_3 and Fe_2O_3 . They employed the host scaffold WO_3 to support a thin layer of Fe_2O_3 on a WO_3 substrate, enabling rapid electron transport across host/guest interfaces (Fig. 15b). They found that increasing the surface area and photon absorption efficiency of Fe_2O_3 increased water oxidation activity. Cobalt oxide (CoO) has been identified as a photocatalyst for H_2 evolution.^{348,349} Liao *et al.*³⁴⁸ demonstrated that CoO nanocrystals can be a photocatalyst for visible-light-induced WS. However, the limited lifetime and rapid

deactivation of CoO nanoparticles prevent their application as a HER photocatalyst.

6.4. Metal sulfides

For decades, CdS and ZnS metal sulfide catalysts have gained the most attention.³⁵¹ CdS is a potential photocatalyst for visible light WS because it has a lower band gap (2.4 eV) than metal oxide semiconductors.¹¹³ However, bare semiconductors have poor H_2 generation rates due to quick photogenerated electron and hole recombination and thus are susceptible to corrosion under light irradiation.³²³ To overcome this issue, other noble metals can be utilized as co-catalysts.³⁵² Huang *et al.*³⁵³ generated a hollow bimetallic sulfide material with a narrow band gap by transferring electrons to the noble metal electronic level or shifting them between the CB of semiconductors. When sensitized with EosinY dye or TiO_2 and g- C_3N_4 semiconductors, it generates the HER at a rate equivalent to platinum. CdS has also been shown to enhance semiconductor activity when used in conjunction with TiO_2 and g- C_3N_4 (ref. 354) as TiO_2 (3.3 eV)

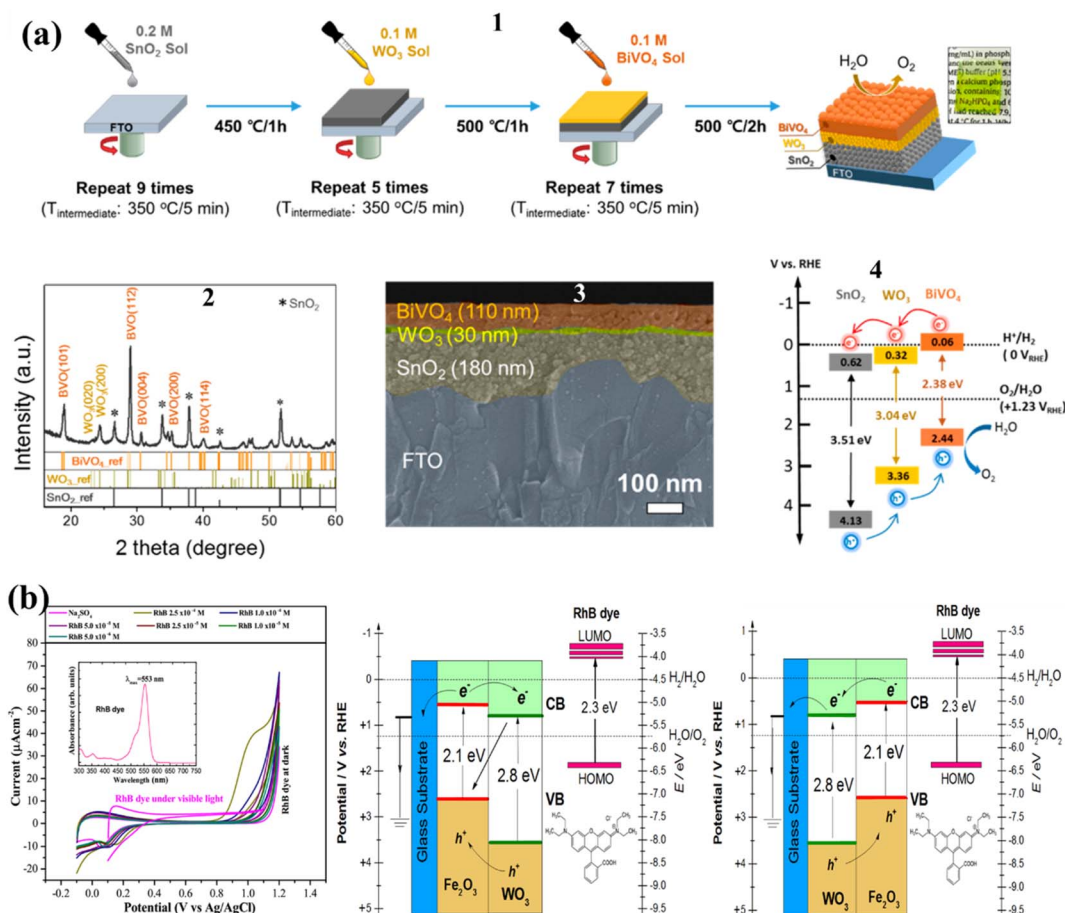


Fig. 15 (a) Preparation and characterization of a triple-layer planar heterojunction (TPH) photoanode composed of $\text{BiVO}_4/\text{WO}_3/\text{SnO}_2$, (1) sol-gel deposition technique. (2) XRD pattern of TPH photoanodes. (3) SEM picture of the improved TPH photoanode in cross-section, demonstrating close contact between layers without any voids. (4) Alignment of the SnO_2 , WO_3 , and BiVO_4 films along with their bands. Adapted from ref. 350. Copyright © 2016, American Chemical Society, (b) cyclic voltammograms (20 mV s^{-1}) for the $\text{FTO}/\text{WO}_3/\text{Fe}_2\text{O}_3$ electrode in the dark, in 0.1 mol L^{-1} Na_2SO_4 aqueous solution, and in supporting electrolytes containing varying concentrations of RhB dye (CV under irradiation in 5.0 10^6 mol L^{-1} RhB dye solution) with the UV-vis RhB absorption spectrum (inset) for comparison. Adapted from ref. 347. Copyright © 2020, Springer Nature.



exhibits a lower response to visible light than CdS (Fig. 16a).³⁵⁵ The photoactivity of ZnS for the HER has been increased. Li *et al.*³⁵⁶ reported using the solid solution systems of $Zn_{1-x}Cd_xS$ to generate the HER under visible light. The band gaps of solid solution photocatalysts can be easily modified by altering the molar ratio of Zn/Cd. Because of the lower band gaps of solid solution photocatalysts, bare ZnS photons absorb more effectively under visible light.³⁵⁷ Furthermore, earlier research has suggested that coupling CdS with large band gap metal oxides such as TaON, TiO_2 , and ZnO might increase the stability of composite materials.^{358,359} Through minimizing charge recombination, various carbon nanostructures may be coupled with CdS to increase WS performance. Any interaction with carbon nanostructures can dramatically increase charge separation due to solid conductivity of CdS. According to the increased catalytic characteristics of nanocomposites, several approaches for developing carbon-based CdS have been investigated, ranging from simple integration of the two components to *in situ* synthesis on the surface of graphene oxide utilizing oxygen

molecules as a template.³⁶⁰ WS_2 -Au-CuInS₂ has been generated for photocatalytic HER performance by sandwiching gold nanoparticles between WS_2 nanotubes and CuInS₂ (CIS) nanoparticles.³⁶¹ The incorporation of Au nanoparticles substantially enhanced visible light absorption. Because of the LSPR impact of Au nanoparticles and the quicker photogenerated carrier separation from Type II band structures, WS_2 -Au-CIS shows the greatest HER performance (Fig. 16b).

6.5. Nitrides

Photocatalysts such as nitrides and oxynitrides can be used to achieve efficient solar light harvesting for WS.³⁶² The energy of the nitrogen 2p orbitals in nitrides is higher than the energy of the oxygen 2p orbitals in metal oxides thus making it easier to excite electrons to the CB in nitrides.³⁶³ Water oxidation is a process that requires a high energy input, and a solid solution of GaN and ZnO has been proposed as a photocatalyst. Both materials have high band gaps and are poorly visible light

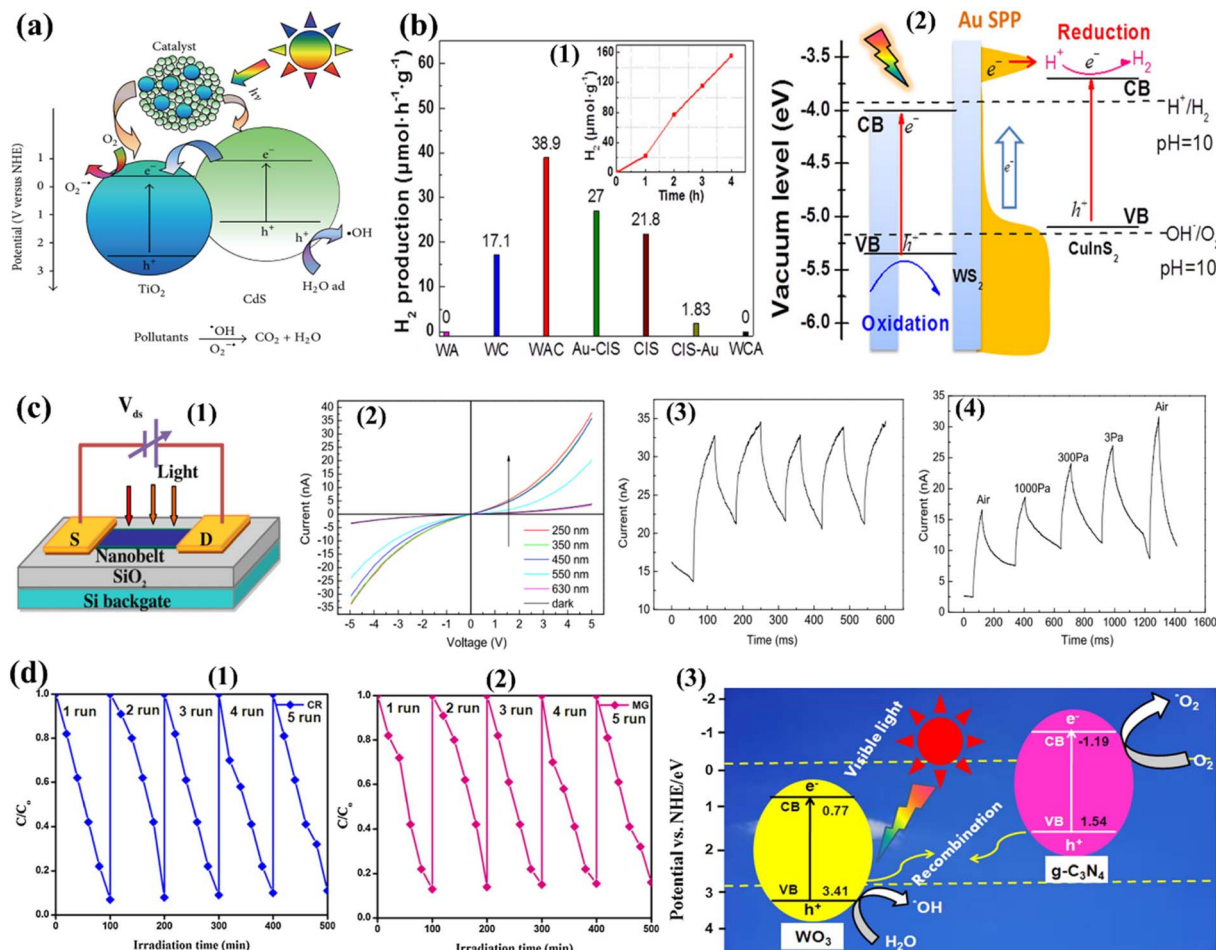


Fig. 16 (a) The possible photocatalytic mechanism of TiO₂/CdS mesoporous microspheres. Adapted from ref. 355. Copyright © 2014, S. Yu *et al.*, (b) (1) the H₂ production plot of WS₂-Au-CIS is shown in the inset. (2) A rough mechanism plan. Adapted from ref. 361. Copyright © 2015, AIP Publishing LLC. (c) (1) The scheme of the photo response is measured using a single Ta₃N₅ nanobelt FET. (2) The *I*-*V* characteristics of the FET when used as a photodetector at different light wavelengths and in the dark. (3) Transient response of Ta₃N₅ nanobelts. (4) The photoreaction of Ta₃N₅ nanobelts irradiated with a 450 nm light pulse at different vacuum and atmospheric pressures, split at a frequency of 100 Hz. Adapted from ref. 377, (d) (1) recycling of a CR; (2) MG using WO₃ and WO₃/g-C₃N₄ catalysts; (3) photocatalytic mechanism of WO₃/g-C₃N₄ catalysts under visible light irradiation. Adapted from ref. 376. Copyright © 2019, Springer Nature.



absorbers. However, after mixing the two materials, new electronic states develop that significantly lower the band gap in a $\text{Ga}_{1-x}\text{Zn}_x$ and N_{1-x}O_x solution.³⁶⁴ Perovskite-like combined oxides of NaTaO_3 and SrTiO_3 are known for their excellent WS performance (Fig. 16c).³⁶⁵ A substitution of one nitrogen atom for an oxygen atom in this compound causes the absorption edge to move toward longer wavelengths (600 nm), which boosts photocatalytic activity. Ta_3N_5 has also been shown to be an effective photocatalyst for WS. Zhen *et al.*³⁶⁶ in 2013 synthesized template-free Ta_3N_5 nanorods doped with $\text{Co}(\text{OH})_x$ and used them as an anode in a PEC WS. Alternatively, Ta_3N_5 has been partially replaced with Mg^{2+} and Zr^{4+} ions to lower the onset potential of PEC water oxidation.³⁶⁷ It is possible to enhance the photocatalytic activity of other semiconductors by similarly modifying their composition. $g\text{-C}_3\text{N}_4$ has been utilized as a photocatalyst for the HER due to its low band gap of 2.7 eV. A sacrificial agent (oxidizing agent) in combination with $g\text{-C}_3\text{N}_4$ could generate H_2 from water at visible light wavelengths without using a noble metal (540 nm). However, bare $g\text{-C}_3\text{N}_4$ is not an efficient photocatalyst. Wang *et al.*³⁶⁸ developed $g\text{-C}_3\text{N}_4$ from cyanamide, which exhibited a visible light absorption edge and continuous stable HER performance over 75 hours. Doping $g\text{-C}_3\text{N}_4$ with non-metal (S, F, B, and P) and metal (Pt, Pd, Fe, Zn, and Cu) atoms has enhanced the photocatalytic activity.^{369–374} Additionally, graphene, carbon nanotubes, and reduced graphene oxide can also be utilized to enhance charge separation in $g\text{-C}_3\text{N}_4$.^{272,375} Furthermore, Sumathi *et al.*³⁷⁶ reported that $\text{WO}_3/g\text{-C}_3\text{N}_4$ heterostructure catalysts synthesized using a one-step microwave irradiation approach exhibited significant visible-light-driven photocatalytic activity (Fig. 16d). $g\text{-C}_3\text{N}_4$ is a versatile photocatalyst that can be used in both PEC cells and solar systems.

6.6. MXene nanosheets

Recently extensive concerns have been raised about the emerging 2D layered transition metal carbides/carbonitrides/nitrides. The first synthesis of transition metal carbides, such as Ti_3C_2 , was reported by Gogotsi *et al.*³⁷⁸ in 2011. The yield of the light-driven HER is limited because photoinduced carriers rush to recombine. MXenes,¹⁵⁷ $g\text{-C}_3\text{N}_4$,³⁷⁹ and reduced graphene oxide³⁸⁰ adaptation are often seen as guest materials to boost the performance of heterogeneous photocatalysts because of their outstanding capability of transferring electrons.^{157,380,381} When MXenes come into contact with other photocatalysts, features including their high SA, many active adsorption sites, and excellent 2D structure help enhance photocatalysis. As seen in the instance of 0D nanomaterial/2D MXene, high metal conductivity is also necessary for stimulating the photocatalytic activity. Additionally, intimate contact enhances physical contact and provides carriers with the possibility to transition from the 0D (functioning as a host) to the 2D MXene interface.^{157,382} T. Su *et al.*¹⁵⁷ analyzed mono- and multi-layer structures of $\text{Ti}_3\text{C}_2\text{TX}$ as cocatalysts for TiO_2 . The H_2 production for the case of a monolayered $\text{Ti}_3\text{C}_2\text{TX}/\text{TiO}_2$ hybrid (abbreviated as 5-TC-TO) structure was $2.6 \text{ mmol h}^{-1} \text{ g}^{-1}$, compared to multi-layered $\text{Ti}_3\text{C}_2\text{TX}/\text{TiO}_2$ (5-MT/TO). It is linked to increased SA in

comparison to multi-layered co-catalysts and the occurrence of monolayer $\text{Ti}_3\text{C}_2\text{TX}/\text{TiO}_2$ active sites. Shortening of distance in the case of the monolayer $\text{Ti}_3\text{C}_2\text{TX}$ is feasible for the rapid migration of photogenerated carriers through the CB of TiO_2 to $\text{Ti}_3\text{C}_2\text{TX}$. Generated holes in the VB through this process are utilized by the hole scavenger. Consequently, a reaction that would lead the H^+ ions to H_2 would be accomplished more easily to effectively utilize the photogenerated charges gathered at the $\text{Ti}_3\text{C}_2\text{TX}$.

Cui *et al.*,³⁸³ outlined the method of transforming Ti_3C_2 MXene into 3D permeable structures of $\text{Ti}_3\text{C}_2\text{-TiO}_2$ nanoflowers. These structures exhibit highly efficient catalysts for the OER, remarkable performance and extended sustainability across a broad range. Notably, the catalysts demonstrated impressive efficiency without requiring the incorporation of any noble metal co-catalyst or sacrificial reagents. The $\text{Ti}_3\text{C}_2\text{-TiO}_2$ nanoflowers have been designed by oxidizing and alkalinizing HF-etched Ti_3C_2 MXene simultaneously, subsequently undergoing ion exchange reactions and annealing procedures (Fig. 17a). Moreover, MXene is a recently developed intermediate for oxide, and in the primarily oxidative Ti_3C_2 MXene, the oxide (TiO_2) is closely related to the Ti_3C_2 MXene component. In this arrangement, the Ti_3C_2 MXene serves as a direct titanium supplier or an interface for transporting photoinduced electrons to improve charging separation performance. Schottky intersections generated by interface contact among Ti_3C_2 MXene and TiO_2 also dramatically speed up the photoexcited separation of charges, whereas TiO_2 absorbs light and supplies electrons as well as holes. Additionally, the nanoflower-like arrangement with 3D porosity can improve photocollection, limit the propagation pathways for photogenerated holes and electrons, increase surface area, and enable the solvent to reach the reactivity areas. In spite of the lack of precious metals (Pt, Au, Ru_2O , *etc.*), such distinctive characteristics associated with developed $\text{Ti}_3\text{C}_2\text{-TiO}_2$ nanoflowers result in substantially improved WS performance for the simultaneous development of H_2 and O_2 sources in a stoichiometric proportion of 2 : 1, without any sacrificial materials (Fig. 17b–g).

6.7. Photocatalytic overall water splitting with immobilized particulate systems

Up until late, using particle suspension systems in laboratories has been the standard method for generating photocatalytic one-step excitation, or Z-scheme OWS. However, the scalability of such WS methods is notably constrained, presenting challenges when attempting to expand particle suspension processes for industrial-scale production. For instance, dispersing a significant amount of particulate photocatalysts within a substantial quantity of water before exposing it to sunlight requires a considerable power supply. One of the obstacles associated with sustaining is getting the photocatalyst powder out of suspension and gathering it. However, a suspension-type reactor cannot monitor the movements of the sun to effectively harvest solar energy. Immobilizing photocatalyst powders on a particular substrate is therefore necessary to enable the upscaling of WS systems from laboratory to





Fig. 17 (a) Diagram showing the steps involved in generating $\text{Ti}_3\text{C}_2\text{-TiO}_2$ nanoflowers, (b and c) HER performance with the existence and without the existence of a co-catalyst using $\text{Ti}_3\text{C}_2\text{-TiO}_2$ nanoflowers fabricated by distinct calcinations, (d) OER performance of $\text{Ti}_3\text{C}_2\text{-TiO}_2$ nanoflowers and (e) TiO_2 nanobelts fabricated by varied calcinations without a co-catalyst along with (f) DRS of the as-prepared materials, and (g) graphical photocatalytic process for TiO_2 nanobelts and $\text{Ti}_3\text{C}_2\text{-TiO}_2$ nanoflowers under solar irradiation. Adapted from ref. 383. Copyright © 2018, Elsevier, (h) the photocatalytic efficiency of a $\text{SrTiO}_3\text{:La, Rh/Au/BiVO}_4$ plate is pH dependent. Charge distributions of $\text{SrTiO}_3\text{:La, Rh/Au/BiVO}_4$ structures (i) before interaction, (j) in the dark during optimum situations, and (k) during band gap stimulation. Adapted from ref. 385. Copyright © 2015, Elsevier.

industrial scales. However, when compared to particle suspension systems, the insufficient diffusion of water to photocatalyst particles and the slow release of gaseous products from the accumulated particle layer present difficulties, often leading to a reduction in photocatalyst performance within fixed particulate systems. As a result, a detailed evaluation of immobilized photocatalyst systems is required for future developments in

order to identify any potential problems related to their practical deployment. The primary endeavor to address particulate photocatalysts for OWS through one-step excitation involved the fabrication of a particulate array utilizing the widely recognized GaN:ZnO photocatalyst.³⁸⁴ A combination of GaN:ZnO photocatalysts modified with $\text{Rh}_{2x}\text{Cr}_x\text{O}_3$ and micrometer-sized silica particles was applied onto a 5×5 cm glass plate using



a drop-casting method. As a result, the photocatalysts fixed to the panel displayed WS activity comparable to that generated through a suspension. The inclusion of silica particles proved to be a crucial factor in enhancing the performance of the photocatalyst panel. This effect is caused by the hydrophilic activity of silica, which causes gaps to form between the photocatalyst particles. This permits water to reach all areas of the photocatalyst and also provides for the efficient release of developed gases. To evaluate the potential of this method, a 1–1 m panel was prepared using the same approach, employing a RhCrO_x -modified Al-doped SrTiO_3 particulate photocatalyst. This panel served as a test module for OWS on a square-meter scale.⁹³ Domen *et al.*³⁸⁵ currently showed that catalyst materials embedded on metallic layers *via* particulate transport move due to the exclusive mechanical and electrical interactions that exist between the particles of semiconductors and the metallic layers, resulting in reduced resistance and increased photocurrent in the photoelectrochemical WS response. Based on these findings, it is anticipated that linking the HEP and OEP with metal conductive surfaces *via* the particulate transport technique will offer a successful way of boosting electron transmission performance and thereby increasing WS performance. Researchers present an all-solid-state system for oxidative mediator-free Z-scheme WS, composed of a plate made of HEP and OEP nanoparticles and a layer of conductivity for effective electron transmission. Using SrTiO_3 :La, Rh, and BiVO_4 as a model, this work explores the efficacy and benefits of all-solid-state design of structures over typical Z-scheme devices using interparticle interaction of electrons for the OWS process (Fig. 17h–k). Unfortunately, the presence of H_2 and O_2 in the reactor poses an obstruction to water diffusion and, in turn, leads to a significant risk of explosion. It is noteworthy that as the WS efficiency reaches a specific threshold, there arises a potential for explosive mixtures of H_2 and O_2 within the panel reactor and it becomes necessary to separate these gases. Nevertheless, a panel-type reactor that integrates a particulate photocatalyst for one-step excitation of OWS has demonstrated promising suitability for large-scale solar H_2 production.

6.8. Metal–organic frameworks (MOFs)

Several advanced catalysts for H_2 generation processes have been developed by researchers, with MOF-based catalysts being one of the foremost potential materials.³⁸⁶ MOFs are assembled from metallic ions and organic compounds, have gained prominence owing to their distinctive porous adaptable framework and large surface area, and are extensively employed in a variety of fields including gas absorption and separation, catalytic processes, energy conservation, and many more. Organic compounds in the molecular framework of MOF-based nanomaterials may act as signals to absorb radiation, be stimulated, and yield hole and electron couples.³⁸⁷ Electrons may go from ligands to metallic complexes and interact with the H^+ , resulting in the photocatalytic HER. Certain metallic sulfides or metallic oxides, including MoS_2 , CdS , and TiO_2 NPs, are additionally frequently employed to increase the photocatalytic performance of MOF-based photocatalysts. Ma *et al.*³⁸⁸ modified

zeolitic imidazolate framework (ZIF)-67 treated with carbon nitride with MoS_2 NPs. Researchers demonstrated that the incorporation of MoS_2 may extend its visible-light absorption capacity and increase the distinction capacity of photoinduced electrons/holes *via* a variety of photoelectric experiments. Furthermore, Pan and colleagues³⁸⁹ synthesized ZIF-8 on titanium dioxide-based hollowed nanospheres (TiO_2 HNPs) using a simple sonochemical method. The effective charge dissociation capability of ZIF-8, as verified through the analysis of photoluminescence (PL), time-resolved photoluminescence (TRPL) decay transient spectra, electrochemical impedance spectra (EIS), and photocurrent (PC) reaction, allows for easy infusion of particles from ZIF-8 to TiO_2 HNPs. This is facilitated by the presence of influential prominent areas offered by ZIF-8. As a result, the catalyst exhibited outstanding ability to yield, with an AQY of up to 50.89% using simulating visible light conditions (Fig. 18a–c). Later, Chen and colleagues³⁹⁰ developed a range of crown-shaped $\text{Zn}_{0.5}\text{Cd}_{0.5}\text{S}$ MTiO_2 hybrids that originated from MOFs. The ideal quantity of the $\text{Zn}_{0.5}\text{Cd}_{0.5}\text{S}$ MTiO_2 hybrid has a higher AQY of 48.9% at 420 nm contrasting to pristine $\text{Zn}_{0.5}\text{Cd}_{0.5}\text{S}$ or M- TiO_2 . Additionally, the HER could exceed $180.4 \text{ mmol g}^{-1} \text{ h}^{-1}$. The significant increase in the photocatalytic function may be attributed mostly to the increased surface area, greater exposure to functional areas, and improved performance in separating electrons and holes (Fig. 18d and e). Similarly, Liu *et al.*³⁹¹ presented a new form of nickel-based MOF singled crystalline material, named Ni-TBAPy-SC, together with its exfoliating nanobelts, referred to as Ni-TBAPy-NB. These materials exhibit excellent stability over a broad spectrum of pH levels in aqueous solutions. Analytical and computational findings suggest that electron transmission from the H4TBAPy compound (light gathering core) to the Ni-O clustering nodes (catalytic core) is possible. This electron transmission may effectively promote WS for producing the HER without the need for a cocatalyst. Exfoliating 2D nanobelts exhibit superior charging isolation as opposed to the individual crystallite. This is due to their reduced charge transmission range and significantly increased reactive surface areas. Therefore, the nanobelts demonstrate a 164-fold increase in water-reducing performance.

6.9. Covalent organic frameworks (COFs)

COFs structurally associated with organic constituent blocks have a high area of surface, an adaptable framework, and high durability.³⁹² COF elements exhibit distinct asymmetries and associations in the context of the photocatalytic HER, as contrasted with MOFs. COFs are a kind of crystallized porous material which are composed of less compact components (including O, C, B, and N) connected by significant covalent bonding.³⁹³ They have a large surface area and may have various shapes based on the functionalities that constitute their organic linkages. Furthermore, the presence of a covalent connection in the COF framework significantly improves its durability. Consequently, it is challenging to transform highly covalently linked COFs into large-scale crystalline materials, leading to a constrained number of regular structural





Fig. 18 (a) Diagram showing the incorporation of double-shell TiO₂/ZIF-8 hollow nanoparticles. (b) The photocatalytic ability for generating the HER of TiO₂ HNPs, ZIF-8, and α -/ β -/ γ -TiO₂/ZIF-8. (c) The operation of the HER over TiO₂/ZIF-8. Adapted from ref. 389. Copyright © 2019, Elsevier, (d) HER of ZCS composites. (e) ZCS-2, M-TiO₂, and varied proportions of ZCS-2/M-TiO₂ mixtures. Adapted from ref. 390. Copyright © 2021, Elsevier.

components.³⁹⁴ The use of solar radiation to facilitate the conversion of water into H₂ and O₂ has been widely recognized as an extremely potential technique to produce environmentally friendly H₂. The processing of photons into chemical energy necessitates the employing of catalysts that possess an appropriate bond arrangement to provide enough reaction possibility.³⁹⁵ Additionally, these photocatalysts must exhibit excellent charge dissociation capability to sustain a constant supply of electrons to the reducing region. COFs possess unique attributes that enable them to fulfill these demands. Multiple studies are being conducted on catalysts based on COFs for the purpose of H₂/O₂ evolution.^{396–398} These studies include the development and regulation of the organic framework. Incorporating electron donor/acceptor ligands with COFs is a useful method for enhancing charge isolation and transmission in COFs.³⁹⁹ Wang *et al.*⁴⁰⁰ transformed a *N*-

acylhydrazone interlinked COF (H-COF) into a durable π -conjugated oxadiazole connected COF (ODA-COF) by performing post-oxidative cyclization of hydrazone coupling. This process resulted in very effective photocatalytic HER, as shown in Fig. 19a and b. The post-synthetic alteration not only increased the spread of π -electrons in the structure, but also enhanced the chemical durability of COFs. This effectively inhibited charging replication and enabled the movement of electrons. When a Pt cocatalyst was used, the ODA-COF material achieved a HER of 2615 $\mu\text{mol g}^{-1} \text{h}^{-1}$, that is more than four-fold the performance seen for the H-COF material connected *via N*-acylhydrazone. Furthermore, Yang *et al.*⁴⁰¹ described the synthesis of a 2D bipyridine-based COF (Bp-COF) that demonstrated the photocatalytic OER. This study constituted the initial instance of imine-interlinked COFs successfully achieving the OER using visible illumination. Bp-COF was





Fig. 19 (a and b) The process for the fabrication and photocatalytic HER of H-COF and ODA-COF. Adapted from ref. 400. Copyright © 2022, John Wiley & Sons, (c) Graphical depiction of the fabrication of Bp-COF, (d) the estimated HOMO/LUMO spectral positions and (e) the photocatalytic OER performance of Bp-COF and BpCo-COF-1. Adapted from ref. 401. Copyright © 2020, Elsevier.

developed by reacting 2,20-bipyridine-5,50-dicarboxaldehyde with 1,3,5-tris(4-aminophenyl)benzene by a chemical process known as Schiff base condensation (Fig. 19c). The feasibility of combining the water oxidation and proton reducing processes in Bp-COF was proven by computational and analytical analysis of its band configuration. In this study, cobalt atoms were incorporated into Bp-COF and bound to the bipyridine patterns to function as the co-catalyst for the photocatalytic OER. When the BpCoCOF-1 material was loaded with 1 wt% Co, it showed a larger HOMO intensity as opposed to the pure Bp-COF material. This increased HOMO intensity may lead to a greater oxidation possibility of the OER, as seen in Fig. 19d. BpCo-COF-1 achieved an outstanding OER of 152 μmol g⁻¹ h⁻¹, as shown in Fig. 19e. The isotopic labelling studies provided additional confirmation that the identified gas originated from the division of water, rather than the degradation of the

catalyst. The catalyst demonstrated its durability in a continuous OER performance study extending over 31 hours.

6.10. Layered double hydroxide (LDH)

LDH-based materials have recently garnered interest due to their distinctive 2D frameworks and the ability to modify their arrangements, as well as their appealing photonic and electrochemical characteristics.^{402,403} These components possess an excellent capacity to adsorb substances and can adjust their band gap. They are good for exchanging cations and anions and can develop distinct locations for oxidation/reduction processes. This allows for the efficient synthesis of H₂/O₂ via the process of WS.⁴⁰⁴ Furthermore, the stacked composition of LDH components enables the incorporation of crystals with diverse dimensions, shapes, and morphologies, in addition to different kinds of anions and cations that constitute its



constitution. These attributes significantly influence the effectiveness of transferring charges and separating, ultimately determining the total efficacy of photocatalytic energy transformation.⁴⁰⁵ Multiple studies have been published to include various facets of LDH fabrication, alterations, and uses. A prime instance may be seen in the research of Fan *et al.*,⁴⁰⁶ which specifically examines the techniques used for developing adaptive LDHs and their subsequent usage as heterogeneous catalysis. In 2016, Mohapatra *et al.*⁴⁰⁴ extensively reviewed 164 references that focused on advancements in the synthesis of LDHs and their use in photocatalytic processes such as photodegradation of dyes, photocatalytic HER, and photoreduction of CO₂ source. In the preceding decade, Yang *et al.*⁴⁰⁷ conducted a comprehensive analysis of the complicated elements that impact the absorbing and the degradation mechanisms of pollutants when LDH nanomaterials are used. In 2018, Wu *et al.*⁴⁰⁸ discussed the progress achieved in developing heterojunctions using LDH. They specifically focused on

the assembly methodologies and the building processes involved in this technique. Megala *et al.*⁴⁰⁹ developed a 2D/2D heterostructure of NiAl-LDH/g-C₃N₄ composites using the *in situ* hydrothermal technique. Researchers subsequently evaluated the photocatalytic efficiency of these composites for H₂ production by WS under simulating light radiation. The NiAl-LDH/g-C₃N₄ composites, after optimization, exhibited a HER of 3170 μmol h⁻¹ g⁻¹, which is the most significant observed estimate for the NiAl-LDH group yet. The improved photocatalytic performance is due to the development of a 2D/2D heterostructure in the NiAl-LDH/g-C₃N₄ composites. This heterostructure allows for effective isolation of electrons/holes when exposed to illumination, resulting in higher electron conductance within the composites (Fig. 20a-c). Similarly, Wang *et al.*⁴¹⁰ developed and assembled a core-shell catalyst consisting of Cu₂O/ZnCr-layered dual hydroxide (LDH) to establish a highly efficient light-activated OWS. The Cu₂O/ZnCr-LDH catalyst demonstrates excellent performance,

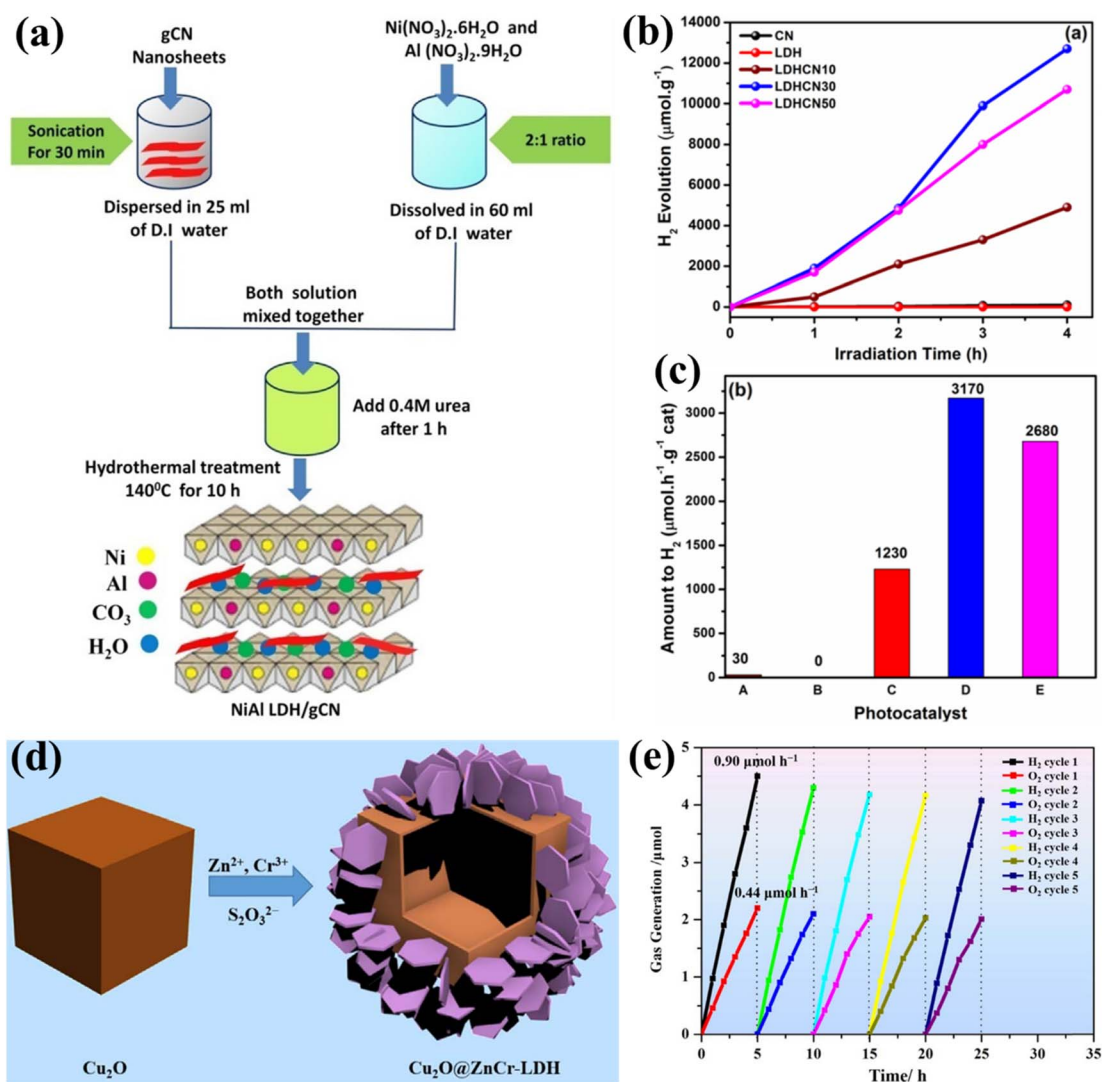


Fig. 20 (a-c) The fabrication procedure and photocatalytic HER of the NiAl LDH/g-C₃N₄ nanocomposite. Adapted from ref. 409. Copyright © 2020, Elsevier, (d and e) graphical depiction of the synthesis and PWOS of Cu₂O/ZnCr-LDH hollowed materials. Adapted from ref. 410. Copyright © 2017, Elsevier.



achieving a significant efficiency with an HER of $0.90 \mu\text{mol h}^{-1}$ and OER of $0.44 \mu\text{mol h}^{-1}$ under visible-light irradiation. Notably, this catalyst does not need a sacrificial reagent or co-catalyst, making it one of the most effective documented catalysts under similar circumstances. The $\text{Cu}_2\text{O}/\text{ZnCr-LDH}$ heterojunction effectively utilizes the synergy impact of Cu_2O and ZnCr-LDH , specifically with regard to aligning their band structures, as shown through empirical and theoretical research. The $\text{S}_2\text{O}_3^{2-}$ cluster located at the terminal of ZnCr-LDH plays a crucial role by effectively mediating between the two elements. This not only prevents the breakdown of Cu_2O under light but also additionally enhances the movement of the photoexcited electrons/holes couple (Fig. 20d and e).

6.11. Chalcogenides

Metallic oxides and chalcogenides are extensively studied as semiconductor compounds that exhibit conducting capacities

transitional among those of conductors and insulators.⁴¹¹ Chalcogenides are materials that consist of several electro-positive components plus a minimum of one chalcogen charge (S^{2-} , Se^{2-} , or Te^{2-}).⁴¹² These materials are recognized due to their small band gap values. These materials are still being studied because of their many desired characteristics, such as a small difference in energy between the highest and lowest energy levels, minimal levels of toxic effects, ability to interact well with living organisms, affordable price, and easy production.⁴¹³ The deployment of chalcogenide based photocatalysts in photocatalytic functions has been extensively determined, mostly due to their small band gap energy, which allows for effective absorption of visible radiation.⁴¹⁴ In more detail, the study of Zhu *et al.*⁴¹⁵ used computational methods employing DFT to demonstrate that single layers of 2D silicon chalcogenides (SiX , where $\text{X} = \text{S}, \text{Se}, \text{Te}$) had band gap values ranging from 2.43 to 3.00 eV. These materials, which are

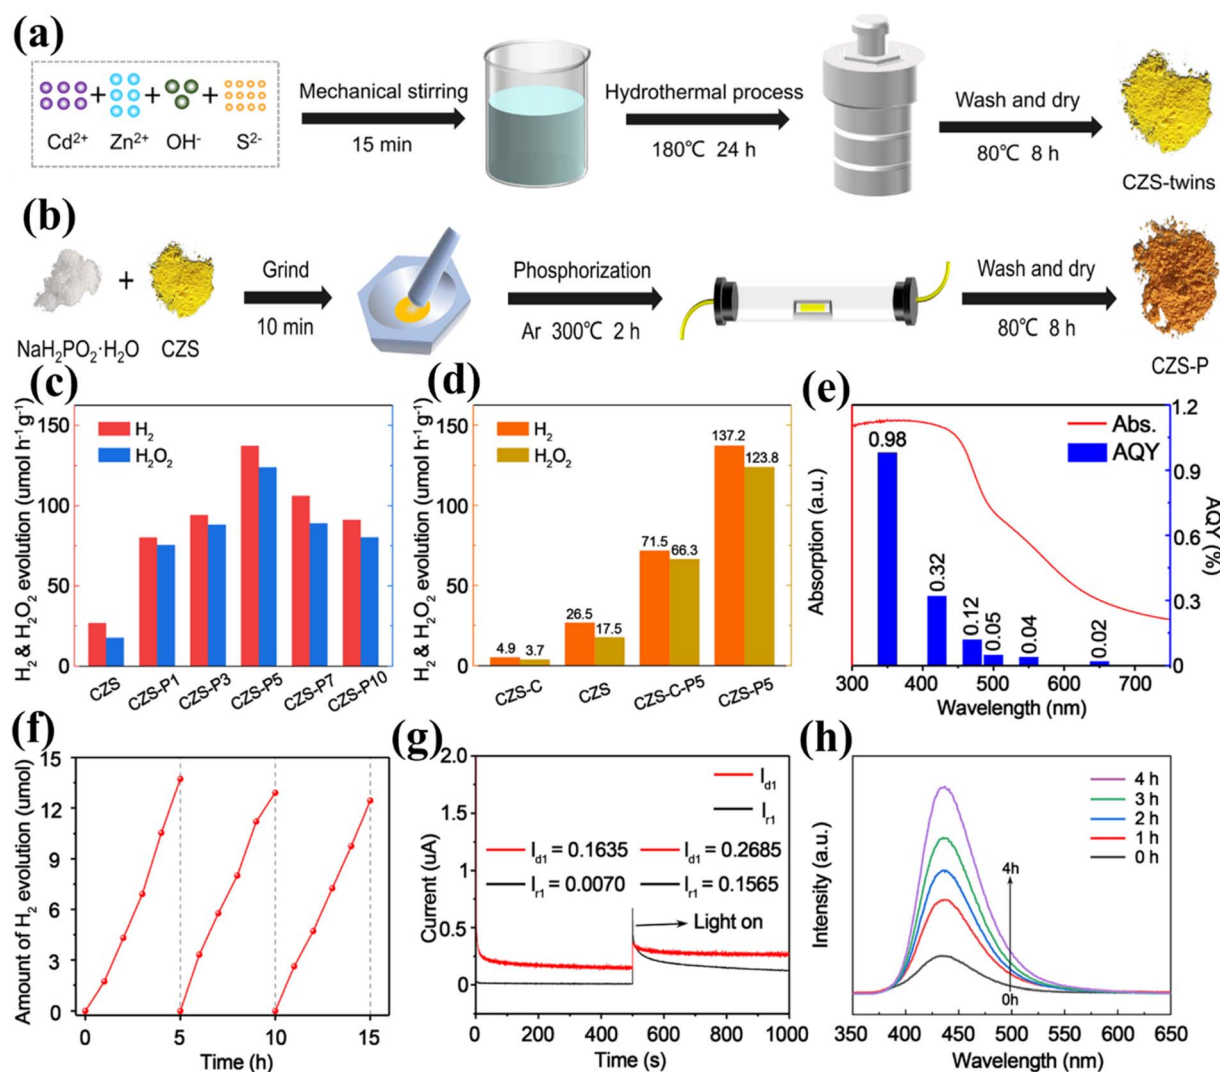


Fig. 21 (a and b) Graphical depiction of the fabrication procedure of CZS and CZS-P, (c) photocatalytic HER and H_2O_2 production from WS using CZS and CZS-P1-10 under visible light illumination, (d) comparison of the photocatalytic performance of all synthesized materials, (e and f) UV-vis AQY and durability assessment of the HER for CZS-P5, and (g) the voltages of the disk electrode (I_{d1}) and ring electrode (I_{r1}) are measured to determine the movement of electron rates across CZS-P5. (h) The PL patterns of the effluent including terephthalic acid measured at a steady state after varying illumination durations. Adapted from ref. 416. Copyright © 2021, American Chemical Society.



semiconductors, also possess advantageous band edge locations that make them suitable for PWS. Optical computations indicate that SiX single layers exhibit significant optical absorbance in the visible-light range. Additionally, the bandgap and band junctions of single layers of silicon chalcogenides may be adjusted by introducing biaxial stress or extending the quantity of the layers, allowing them to better correspond to the reactive potentials of water. The 2D SiX exhibits a combination of electrical characteristics, significant carrier accessibility, and optical characteristics, making it a very potential catalyst for WS. Liu *et al.*⁴⁴⁶ presented the surface phosphorization of CZS nanotwins, which exhibit significant erosion strength for photocatalytic WS. This process enables simultaneous synthesis of H₂ and H₂O₂ without the need for any co-catalyst or sacrificial reagent. The effectiveness of the process relies on the integrated impact of coherence dual surfaces inside the main compound, which facilitates effective separation of charges, interface P bridging that enables fast charging movement, and the presence of red phosphorus (RP) on the outermost layer as potential areas for H₂O₂ formation. The process included two main phases that produced surface phosphatized CZS nanotwin materials. First, CZS nanotwins were synthesized using a hydrothermal approach. Subsequently the nanotwins were phosphorized by subjecting them to combustion of NaH₂PO₂·H₂O, as illustrated in Fig. 21a and b. Adding NaOH during the hydrothermal procedure will cause the metallic ions to precipitate earlier. Under these circumstances, the degree to which the metallic ions are released and sulfurized would decrease, hence facilitating the development of nanotwins. In the presence of an

argon environment, the PH₃ gas produced by the thermal decomposition of NaH₂PO₂·H₂O will undergo a reaction with CZS nanotwins, resulting in the formation of a P loaded CZS nanotwin material on the surface. Photocatalytic experiments were then performed to investigate the potential of such materials for WS under visible illumination exposure, with no need for any sacrificial reagent. Fig. 21c demonstrates that the pure CZS nanotwins showed a modest performance of approximately 26.5 μmol h⁻¹ g⁻¹ for the HER from WS. During the phosphating procedure, the HER observed a substantial prominence and achieved its peak activities of 137.2 μmol h⁻¹ g⁻¹ across the CZSP5 material despite the use of any co-catalyst. This activity level is approximately 27-fold higher compared to that of typical CZS-C, as seen in Fig. 21d. The AQY values at various wavelengths are displayed in Fig. 21e. Remarkably, CZS-P5 also exhibited outstanding durability under these reaction conditions. There was no noticeable decrease in the photocatalytic function detected throughout a 15-hour test period (Fig. 21f). The findings of the RRDE investigation are shown in Fig. 21g. The transmitted electron ratio for CZS-P5 nanotwins was shown to be about 2, confirming the occurrence of a two-electron interaction channel in the photocatalytic process of WS, leading to the generation of H₂O₂. To comprehend the probable process of H₂O₂ generation, researchers conducted additional investigations on the associated reactive components. The presence of ·OH radicals was identified using a PI technique that relies on the interaction involving ·OH and terephthalic acid (Fig. 21h). Similarly, the photocatalytic performances of different photocatalysts along with stability depiction are shown in Table 1.

Table 1 The photocatalytic performance of different photocatalysts along with stability depiction

Photocatalysts	HER	OER	Stability	References
Au-NiO _x /TiO ₂	18.3 μmol h ⁻¹ g ⁻¹	9 μmol h ⁻¹ g ⁻¹	Good	247
NiO-SrTiO ₃	240 μmol h ⁻¹ g ⁻¹	130 μmol h ⁻¹ g ⁻¹	Fair	417
CaTaO ₂ N	6.5 μmol h ⁻¹ g ⁻¹	3.2 μmol h ⁻¹ g ⁻¹	Good	418
Ni/Sr ₂ Nb ₂ O ₇	6.7 μmol h ⁻¹ g ⁻¹	3.3 μmol h ⁻¹ g ⁻¹	Good	419
Cu ₂ O@ZnCr-LDH	0.90 μmol h ⁻¹	0.44 μmol h ⁻¹	Excellent	420
Co-Pi/Bi-La ₂ Ti ₂ O ₇ /Pt	66.6 μmol	32.1 μmol	Good	421
GDY/g-C ₃ N ₄ -VN	0.48 μmol h ⁻¹	0.24 μmol h ⁻¹	Good	422
Pt/g-C ₃ N ₄	61 μmol h ⁻¹ g ⁻¹	31.5 μmol h ⁻¹ g ⁻¹	Excellent	184
GaFeO ₃	9.0 μmol h ⁻¹ g ⁻¹	4.5 μmol h ⁻¹ g ⁻¹	Fair	423
NiO/NaTaO ₃ :La	5900 μmol h ⁻¹ g ⁻¹	2900 μmol h ⁻¹ g ⁻¹	Fair	424
Al-CuS/ZIS	153.6 μmol h ⁻¹ g ⁻¹	73.1 μmol h ⁻¹ g ⁻¹	Good	425
BiVO ₄ -Ru/SrTiO ₃ :Rh	40.1 μmol h ⁻¹ g ⁻¹	18.6 μmol h ⁻¹ g ⁻¹	Fair	96
Pt/KCa ₂ Nb ₃ O ₁₀	260 μmol h ⁻¹ g ⁻¹	120 μmol h ⁻¹ g ⁻¹	Good	426
CDots/CoO	33.4 μmol h ⁻¹ g ⁻¹	18.2 μmol h ⁻¹ g ⁻¹	Good	427
Pt/CdS@Al ₂ O ₃	62.2 μmol h ⁻¹ g ⁻¹	27.3 μmol h ⁻¹ g ⁻¹	Good	428
Ba ₂ In ₂ O ₅ /In ₂ O ₃	58.6 μmol h ⁻¹ g ⁻¹	30.4 μmol h ⁻¹ g ⁻¹	Excellent	429
Cu ₂ O/ZnCr-LDH	45 μmol h ⁻¹ g ⁻¹	22 μmol h ⁻¹ g ⁻¹	Good	410
Co ₁ -phosphide/PCN	410.3 μmol h ⁻¹ g ⁻¹	204.6 μmol h ⁻¹ g ⁻¹	Good	430
Pt-loaded Mg/TiO ₂	850 μmol h ⁻¹ g ⁻¹	425 μmol h ⁻¹ g ⁻¹	Good	431
Pt/GaN NWs	29.4 μmol h ⁻¹	16.4 μmol	Good	432
FeCoPi/Bi ₄ NbO ₈ Cl-OVs	2.5 μmol h ⁻¹	1.3 μmol h ⁻¹	Good	433
RuO ₂ /GaN:ZnO	3200 μmol h ⁻¹ g ⁻¹	(1500) ⁵ μmol h ⁻¹ g ⁻¹	Fair	434
CQDs/Ag/Ag ₃ PW ₁₂ O ₄₀	8.04 μmol h ⁻¹ g ⁻¹	4.02 μmol h ⁻¹ g ⁻¹	Good	435
ZnRh ₂ O ₄ /Ag/Bi ₄ V ₂ O ₁₁	0.25 μmol h ⁻¹ g ⁻¹	0.089 μmol h ⁻¹ g ⁻¹	Good	436
CoO/g-C ₃ N ₄	50.2 μmol h ⁻¹ g ⁻¹	27.8 μmol h ⁻¹ g ⁻¹	Good	437





Fig. 22 The PWS in the heptazine–water complex, according to Domcke and Sobolewski. Adapted from ref. 457. Copyright © 2013, Royal Society of Chemistry.

7. Photocatalytic water splitting: a theoretical modeling approach

Light absorption,⁴³⁸ electron/hole transport,⁴³⁹ semiconductor band edge alignment,⁴⁴⁰ and surface photo redox chemistry⁴⁴¹ have all been theoretically studied and have predictive capacity, low processing cost, and reproducibility. Density functional theory (DFT) is commonly used to predict and explain the electrical structure of materials due to its excellent accuracy.⁴⁴² However, a significant disadvantage of DFT is its inability to forecast band gaps due to poor self-interaction and correlation accurately. To address this issue, hybrid functionals or the injection of electron repulsion into a subset of localized orbitals is a practical way.^{443,444} Although hybrid functions are more accurate than classic exchange and correlation functions for predicting band gaps and locating excited states, they are computationally costly.^{445,446} The most successful technique for solving the band gap problem is known as many-body perturbation theory (MBPT).^{447,448} Although this method is computationally costly, it sets a baseline for comparative research, which can aid in the development of new methods.^{445,449} The most recent approach, TB09, combines the modified exchange capacity of Becke–Johnson with an LDA correlation.^{450,451} When combined with variants, this strategy has been proven to be one of the most cost-effective approaches to date.^{445,452} Computational approaches are beneficial for anticipating impurity states produced by doping in photocatalytic systems such as TiO₂.⁴⁵³ The bulk of studies rely on cluster-based models rather than time-dependent density functional theory (TD-DFT) as shown in the computational investigation of the photoinduced homolytic dissociation of water in the pyridine–water complex (Fig. 22). In

addition to predictions, theoretical and computational techniques may enable us to properly comprehend state features. The investigated topics include the band structures and densities of the BiVO₄ state, the electron/hollow production process, and the mobility and energy level of the surface processes. BiVO₄ addresses the photoinduced electrons and light on various crystal-like facets. According to computer studies, the (010) facets have a low energy absorption of over 420 nm, a faster transit electron/hole, faster water absorption, and a low OER energy potential. These theoretical studies can potentially improve the band structure and morphology of photocatalytic materials. Accuracy gains and processing cost reductions should lead to the development of high-throughput computational screening. This will reduce significantly the amount of time required to find novel materials, which will help in component selection. There have been suggestions for quick screening techniques to find photocatalytic compounds, such as SEM and multiplex counter electrodes.⁴⁵⁴ Further evidence that significant studies in this field may soon develop comes from the scarce and recent computer screening investigations of photoactive materials.^{455,456}

8. Conclusions

In recent studies, Photocatalytic overall water splitting (POWS) vitality seems promising to produce green energy. The latest developments in the field of POWS have clearly shown that using composites or heterostructures in photocatalysts has great potential for solar-driven water splitting (WS). To meet the standards for POWS, a photocatalyst (possessing specific characteristics) may be a single photocatalyst or combined with semiconductors to achieve one or two-step excitation.



Regarding this, the photocatalyst bandgap must be in the range of 1.23 eV to 3.1 eV, and be capable of facilitating water reduction and oxidation reactions. The POWS method may use photocatalysts capable of using visible light to either decrease or oxidize water. To accomplish optimal one/two-step excitation and Z-scheme OWS, it is necessary to use functional charged separation approaches such as interface junction, structurally charging isolation, and linearly polarized charging dissociation procedures. This article provides a description of the parameters used to appropriately assess the catalytic efficiency, apparent quantum yield (AQY), and solar-to-hydrogen (STH) energy utilization. Furthermore, it examines the present progress in synthesizing of novel light-absorbing photocatalysts and offers insights and methodologies for separating photoexcited charges. This review examines multiple aspects of development, including chemical and physical transformations, environmental influences, numerous kinds of photocatalysts, and specific variables that influence PWS. Primary factors for attaining an effective photocatalytic reaction encompassing of adverse situations to high light adsorption phenomenon, and the developed structures at nanoscale.

Although significant advancements have been made in this field of study, it currently confronts several apparent limitations.

(1) Defect engineering is considered a simple and promising technique for tuning the bandgap structure of semiconductors. A cocatalyst is essential to accelerate the reaction while minimizing the risk of the reverse reaction. However, suppressing the recombination of the charges remains a challenging task. Recently, some methods have been proposed to extend the excitation lifetime of electron-hole pairs by generating an internal electric field. Another effective way to accomplish charge suppression is by elevating the temperature (*via* solar means). This increases ionic dissociation at elevated temperatures, leading to an increase in H^+ and OH^- ions. These ions generate a local electric field (LEF) in the surrounding region, to prolong the exciton lifetimes of the photocatalysts. The LEF can also be enhanced by considering materials with polar-faceted properties, (*e.g.*, PFO or LDH, holding strong polarity in the vicinity of the material surface. The aforementioned method can suppress charge recombination, subsequently enhancing quantum efficiencies (QEs).

(2) The simplicity and cost-effectiveness of a particulate PWS system give it an advantage over solar energy conversion, such as photoelectrochemical devices and photovoltaic-electrolysis systems. However, the H_2 conversion efficiency of a particulate PWS system is currently only around 1%. Therefore, future studies will focus on improving the efficiency by at least up to 5% to meet the demand for practical application.²⁴⁰ The development of new strategies that utilize not only visible but also infrared light is highly essential.

(3) Also, novel approaches capable of suppressing the recombination of charge carriers and reverse reactions are also crucial. Developing a comprehensive understanding of the interrelated processes involved in H_2 fuel production, including purification, separation, transportation, and hydrogen fuel consumption, remains challenging. All these factors are

essential in understanding problems and their solutions to produce sustainable and efficient H_2 production sources driven by solar-light WS.

(4) An overview of the most recent significant studies on semiconductor-based materials, focusing on fabrication, design, and photocatalytic applications of various nanocomposites, has been provided. Although the coupling of semiconductors has been shown to increase the photocatalytic efficiency of the photocatalysts, the overall photocatalytic performance of sunlight still needs to be improved. Several methods based on the development of semiconductor-based materials can be implemented in future studies:

(i) The surface area of bulk semiconductor materials is typically small. To enhance the photocatalytic performance of these materials, future studies should focus on increasing the SA by synthesizing semiconductors by employing a template-assisted method. Other factors that affect the photocatalytic properties, (*e.g.*, bandgap design, composition, and morphology), also need to be investigated in detail. Increasing the SA is critical to improving photocatalytic performance by providing more active sites and increasing charge separation.

(ii) The fundamental understanding of the charge transport process and mechanisms in nanocomposites based on semiconductor materials has remained a challenging task until now. Several factors influencing the process must be comprehended, such as the dynamics of photogenerated carriers on the surface and the interface between semiconductors, as well as defect formation at the interface due to mismatches in semiconductor band alignments.

(iii) The toxicological assessment of semiconductor-based nanocomposites is a critical issue that requires attention. To enable the development of nanocomposites for various photocatalytic applications, further research is necessary on both *in vitro* and *in vivo* studies of semiconductor-based nanocomposites on living organisms.

(iii) Finally, developing low-cost, non-toxic, environmentally friendly materials and novel strategies to improve photocatalyst's charge separation and sunlight absorption are critical for conducting a successful photocatalysis using solar semiconductor materials. In view of the discussed challenges, the commercial application of semiconductor-based nanocomposites in the HER through WS, organic wastewater treatment, and bacterial disinfected carbon photoreductions would undoubtedly produce more promising outcomes.

Conflicts of interest

There are no conflicts of interest to declare.

Acknowledgements

The authors extend their appreciation to the Deanship of Scientific Research at King Khalid University for funding this work through small group Research Project under grant number (RGP. 1/336/44). We gratefully acknowledge the support of this research by funding from the Foundation of



Yangtze Delta Region Institute (Huzhou) of UESTC, China, (No. U03210057).

References

- H.-T. Pao and C.-M. Tsai, *Energy Policy*, 2010, **38**, 7850–7860.
- A. Qadeer, S. Liu, M. Liu, X. Liu, Z. Ajmal, Y. Huang, Y. Jing, S. K. Khalil, D. Zhao and D. Weining, *J. Cleaner Prod.*, 2019, **231**, 1070–1078.
- A. Hayat, M. Sohail, U. Anwar, T. Taha, K. S. El-Nasser, A. M. Alenad, A. G. Al-Sehemi, N. A. Alghamdi, O. A. Al-Hartomy and M. A. Amin, *J. Colloid Interface Sci.*, 2022, **624**, 411–422.
- M. Sohail, T. Altalhi, A. G. Al-Sehemi, T. A. M. Taha, K. S. El-Nasser, A. A. Al-Ghamdi, M. Boukhari, A. Palamanit, A. Hayat and M. A. Amin, *Nanomaterials*, 2021, **11**, 3245.
- F. Pan, M. Sohail, T. Taha, A. G. Al-Sehemi, S. Ullah, H. S. ALSalem, G. A. Mersal, M. M. Ibrahim, A. M. Alenad and O. A. Al-Hartomy, *Mater. Res. Bull.*, 2022, **152**, 111865.
- S. J. Davis and K. Caldeira, *Proc. Natl. Acad. Sci. U. S. A.*, 2010, **107**, 5687.
- D. Dodman, *Environ. Urbanization*, 2009, **21**, 185–201.
- A. Hayat, M. Sohail, A. G. Al-Sehemi, N. A. Alghamdi, T. Taha, H. S. ALSalem, A. M. Alenad, M. A. Amin, A. Palamanit and C. Liu, *Int. J. Hydrogen Energy*, 2022, **47**, 14280–14293.
- S. J. A. Moniz, S. A. Shevlin, D. J. Martin, Z.-X. Guo and J. Tang, *Energy Environ. Sci.*, 2015, **8**, 731–759.
- J. Byrne, K. Hughes, W. Rickerson and L. Kurdgelashvili, *Energy Policy*, 2007, **35**, 4555–4573.
- R. Di Primio, B. Horsfield and M. A. Guzman-Vega, *Nature*, 2000, **406**, 173–176.
- A. M. Alenad, T. Taha, M. A. Amin, A. Irfan, J. Oliva, Y. Al-Hadeethi, A. Palamanit, A. Hayat, S. K. B. Mane and M. Sohail, *J. Photochem. Photobiol., A*, 2022, **423**, 113591.
- A. Hayat, M. Sohail, W. Iqbal, T. Taha, A. M. Alenad, A. G. Al-Sehemi, S. Ullah, N. A. Alghamdi, A. Alhadhrami and Z. Ajmal, *J. Sci.: Adv. Mater. Devices*, 2022, **7**, 100483.
- A. Qadeer, Z. A. Saqib, Z. Ajmal, C. Xing, S. Khan Khalil, M. Usman, Y. Huang, S. Bashir, Z. Ahmad, S. Ahmed, K. H. Thebo and M. Liu, *Sustainable Cities Soc.*, 2020, **53**, 101959.
- E. Barbier, *Renewable Sustainable Energy Rev.*, 2002, **6**, 3–65.
- H.-W. Sinn, *The Green Paradox: a Supply-Side Approach to Global Warming*, MIT press, 2012.
- A. Hayat, M. Sohail, T. Taha, A. M. Alenad, A. Irfan, N. Shaishta, A. Hayat, S. K. B. Mane and W. U. Khan, *CrystEngComm*, 2021, **23**, 4963–4974.
- A. Hayat, M. Sohail, A. El Jerry, K. M. Al-Zaydi, S. Raza, H. Ali, Y. Al-Hadeethi, T. Taha, I. U. Din and M. A. Khan, *Mater. Today*, 2023, **64**, 180–208.
- B. Parida, S. Iniyana and R. Goic, *Renewable Sustainable Energy Rev.*, 2011, **15**, 1625–1636.
- W. T. Xie, Y. J. Dai, R. Z. Wang and K. Sumathy, *Renewable Sustainable Energy Rev.*, 2011, **15**, 2588–2606.
- C. Zamfirescu, I. Dincer, G. F. Naterer and R. Banica, *Chem. Eng. Sci.*, 2013, **97**, 235–255.
- L. Wang, Y. Zhang, L. Chen, H. Xu and Y. Xiong, *Adv. Mater.*, 2018, **30**, 1801955.
- P. Niu, J. Dai, X. Zhi, Z. Xia, S. Wang and L. Li, *InfoMat*, 2021, **3**, 931–961.
- B. Han, S. Liu, N. Zhang, Y.-J. Xu and Z.-R. Tang, *Appl. Catal., B*, 2017, **202**, 298–304.
- K.-Q. Lu, M.-Y. Qi, Z.-R. Tang and Y.-J. Xu, *Langmuir*, 2019, **35**, 11056–11065.
- S. Chen, T. Takata and K. Domen, *Nat. Rev. Mater.*, 2017, **2**, 1–17.
- K. Domen, S. Naito, M. Soma, T. Onishi and K. Tamaru, *J. Chem. Soc. Chem. Commun.*, 1980, 543–544, DOI: [10.1039/C39800000543](https://doi.org/10.1039/C39800000543).
- L. Yuan, C. Han, M.-Q. Yang and Y.-J. Xu, *Int. Rev. Phys. Chem.*, 2016, **35**, 1–36.
- A. Fujishima and K. Honda, *Nature*, 1972, **238**, 37–38.
- J. Li, R. Güttinger, R. Moré, F. Song, W. Wan and G. R. Patzke, *Chem. Soc. Rev.*, 2017, **46**, 6124–6147.
- Y. Fang, Y. Hou, X. Fu and X. Wang, *Chem. Rev.*, 2022, **122**, 4204–4256.
- J. P. McEvoy and G. W. Brudvig, *Chem. Rev.*, 2006, **106**, 4455–4483.
- M. Xuan and J. Li, *Natl. Sci. Rev.*, 2021, **8**, nwab051.
- D. G. Nocera, *Acc. Chem. Res.*, 2012, **45**, 767–776.
- Y. Umena, K. Kawakami, J.-R. Shen and N. Kamiya, *Nature*, 2011, **473**, 55–60.
- C. Zhou, R. Shi, G. I. Waterhouse and T. Zhang, *Coord. Chem. Rev.*, 2020, **419**, 213399.
- C. Bie, L. Wang and J. Yu, *Chem*, 2022, **8**, 1567–1574.
- J. H. Kim, D. Hansora, P. Sharma, J.-W. Jang and J. S. Lee, *Chem. Soc. Rev.*, 2019, **48**, 1908–1971.
- J. Schneider, M. Matsuoka, M. Takeuchi, J. Zhang, Y. Horiuchi, M. Anpo and D. W. Bahnemann, *Chem. Rev.*, 2014, **114**, 9919–9986.
- X. Tao, Y. Zhao, S. Wang, C. Li and R. Li, *Chem. Soc. Rev.*, 2022, **51**, 3561–3608.
- Q. Wang and K. Domen, *Chem. Rev.*, 2019, **120**, 919–985.
- Z. Wang, T. Hisatomi, R. Li, K. Sayama, G. Liu, K. Domen, C. Li and L. Wang, *Joule*, 2021, **5**, 344–359.
- R. Li and C. Li, in *Advances in Catalysis*, Elsevier, 2017, vol. 60, pp. 1–57.
- K. H. Ng, S. Y. Lai, C. K. Cheng, Y. W. Cheng and C. C. Chong, *Chem. Eng. J.*, 2021, **417**, 128847.
- W. Zhou and H. Fu, *Inorg. Chem. Front.*, 2018, **5**, 1240–1254.
- K. Takane and K. Domen, *ChemCatChem*, 2012, **4**, 1485–1497.
- K. Rajeshwar, A. Thomas and C. Janáky, *J. Phys. Chem. Lett.*, 2015, **6**, 139–147.
- M.-Y. Qi, M. Conte, M. Anpo, Z.-R. Tang and Y.-J. Xu, *Chem. Rev.*, 2021, **121**, 13051–13085.
- L. Tian, X. Guan, S. Zong, A. Dai and J. Qu, *Catalysts*, 2023, **13**, 355.
- M. Qureshi, A. T. Garcia-Esparza, G. Jeantelot, S. Ould-Chikh, A. Aguilar-Tapia, J.-L. Hazemann, J.-M. Basset, D. Loffreda, T. Le Bahers and K. Takane, *J. Catal.*, 2019, **376**, 180–190.



- 51 M. A. Nadeem, M. A. Khan, A. A. Ziani and H. Idriss, *Catalysts*, 2021, **11**, 60.
- 52 A. Kudo and Y. Miseki, *Chem. Soc. Rev.*, 2009, **38**, 253–278.
- 53 A. L. Linsebigler, G. Lu and J. T. Yates, *Chem. Rev.*, 1995, **95**, 735–758.
- 54 Z. Zou, J. Ye, K. Sayama and H. Arakawa, *Nature*, 2001, **414**, 625–627.
- 55 A. Hayat, M. Sohail, U. Anwar, T. Taha, H. Qazi, Amina, Z. Ajmal, A. G. Al-Sehemi, H. Algarni and A. A. Al-Ghamdi, *Chem. Rec.*, 2023, **23**, e202200143.
- 56 A. Hayat, M. Sohail, A. Qadeer, T. Taha, M. Hussain, S. Ullah, A. G. Al-Sehemi, H. Algarni, M. A. Amin and M. Aqeel Sarwar, *Chem. Rec.*, 2022, **22**, e202200097.
- 57 M. Sohail, J. Huang, Z. Lai, Y. Cao, S. Ruan, M. N. Shah, F. U. Khan, H. I. A. Qazi and B. Ullah, *J. Inorg. Organomet. Polym. Mater.*, 2020, **30**, 5168–5179.
- 58 A. Hayat, M. Sohail, A. El Jery, K. M. Al-Zaydi, S. Raza, H. Ali, Z. Ajmal, A. Zada, T. Taha and I. U. Din, *Energy Storage Mater.*, 2023, 102780.
- 59 T. Song, J. Wang, L. Su, H. Xu, X. Bai, L. Zhou and W. Tu, *Mol. Catal.*, 2021, **516**, 111939.
- 60 V. Etacheri, C. Di Valentin, J. Schneider, D. Bahnemann and S. C. Pillai, *J. Photochem. Photobiol., C*, 2015, **25**, 1–29.
- 61 M. Gratzel, *Energy resources through photochemistry and catalysis*, Elsevier, 2012.
- 62 W. Wu, C. Jiang and V. A. Roy, *Nanoscale*, 2015, **7**, 38–58.
- 63 H. Yoneyama, H. Sakamoto and H. Tamura, *Electrochim. Acta*, 1975, **20**, 341–345.
- 64 M. Ni, M. K. H. Leung, D. Y. C. Leung and K. Sumathy, *Renewable Sustainable Energy Rev.*, 2007, **11**, 401–425.
- 65 K. Takanebe, *ACS Catal.*, 2017, **7**, 8006–8022.
- 66 K. Sivula and R. van de Krol, *Nat. Rev. Mater.*, 2016, **1**, 15010.
- 67 B. Yan, P. Zhou, Q. Xu, X. Zhou, D. Xu and J. Zhu, *RSC Adv.*, 2016, **6**, 6133–6137.
- 68 M. Reticcioli, U. Diebold, G. Kresse and C. Franchini, *Handbook of Materials Modeling*, Springer Nature Switzerland AG, 2020, pp. 1035–1073.
- 69 J. K. Cooper, S. Gul, F. M. Toma, L. Chen, P.-A. Glans, J. Guo, J. W. Ager, J. Yano and I. D. Sharp, *Chem. Mater.*, 2014, **26**, 5365–5373.
- 70 W. Lu, D. Yuan, J. Sculley, D. Zhao, R. Krishna and H.-C. Zhou, *J. Am. Chem. Soc.*, 2011, **133**, 18126–18129.
- 71 A. Kudo, K. Ueda, H. Kato and I. Mikami, *Catal. Lett.*, 1998, **53**, 229–230.
- 72 V. I. Merupo, S. Velumani, G. Oza, M. Tabellout, M. Bizarro, S. Coste and A. H. Kassiba, *ChemistrySelect*, 2016, **1**, 1278–1286.
- 73 J. E. Yourey and B. M. Bartlett, *J. Mater. Chem. A*, 2011, **21**, 7651–7660.
- 74 K. J. McDonald and K.-S. Choi, *Chem. Mater.*, 2011, **23**, 4863–4869.
- 75 S. Ida, K. Yamada, T. Matsunaga, H. Hagiwara, Y. Matsumoto and T. Ishihara, *J. Am. Chem. Soc.*, 2010, **132**, 17343–17345.
- 76 R. Patil, S. Kelkar, R. Naphade and S. Ogale, *J. Mater. Chem. A*, 2014, **2**, 3661–3668.
- 77 P. Zhang, J. Zhang and J. Gong, *Chem. Soc. Rev.*, 2014, **43**, 4395–4422.
- 78 M. Higashi, K. Domen and R. Abe, *J. Am. Chem. Soc.*, 2012, **134**, 6968–6971.
- 79 J. Zhao, T. Minegishi, L. Zhang, M. Zhong, Gunawan, M. Nakabayashi, G. Ma, T. Hisatomi, M. Katayama, S. Ikeda, N. Shibata, T. Yamada and K. Domen, *Angew. Chem., Int. Ed.*, 2014, **53**, 11808–11812.
- 80 L. Zhang, T. Minegishi, M. Nakabayashi, Y. Suzuki, K. Seki, N. Shibata, J. Kubota and K. Domen, *Chem. Sci.*, 2015, **6**, 894–901.
- 81 M. Moriya, T. Minegishi, H. Kumagai, M. Katayama, J. Kubota and K. Domen, *J. Am. Chem. Soc.*, 2013, **135**, 3733–3735.
- 82 B. Seger, A. B. Laursen, P. C. K. Vesborg, T. Pedersen, O. Hansen, S. Dahl and I. Chorkendorff, *Angew. Chem., Int. Ed.*, 2012, **51**, 9128–9131.
- 83 J. Zhang, M. Zhang, R.-Q. Sun and X. Wang, *Angew. Chem., Int. Ed.*, 2012, **51**, 10145–10149.
- 84 C. Liu, J. Sun, J. Tang and P. Yang, *Nano Lett.*, 2012, **12**, 5407–5411.
- 85 R. Li, *Chin. J. Catal.*, 2017, **38**, 5–12.
- 86 X. Li, J. Yu, J. Low, Y. Fang, J. Xiao and X. Chen, *J. Mater. Chem. A*, 2015, **3**, 2485–2534.
- 87 J. M. Bolts and M. S. Wrighton, *J. Phys. Chem.*, 1976, **80**, 2641–2645.
- 88 K. Maeda and K. Domen, *J. Phys. Chem. Lett.*, 2010, **1**, 2655–2661.
- 89 N. Serpone, *J. Photochem. Photobiol., A*, 1997, **104**, 1–12.
- 90 A. Kudo and Y. Miseki, *Chem. Soc. Rev.*, 2009, **38**, 253–278.
- 91 F. Wagner and G. Somorjai, *J. Am. Chem. Soc.*, 1980, **102**, 5494–5502.
- 92 K. Domen, S. Naito, M. Soma, T. Onishi and K. Tamaru, *J. Chem. Soc. Chem. Commun.*, 1980, 543–544.
- 93 Y. Goto, T. Hisatomi, Q. Wang, T. Higashi, K. Ishikiriyama, T. Maeda, Y. Sakata, S. Okunaka, H. Tokudome and M. Katayama, *Joule*, 2018, **2**, 509–520.
- 94 Y. Ham, T. Hisatomi, Y. Goto, Y. Moriya, Y. Sakata, A. Yamakata, J. Kubota and K. Domen, *J. Mater. Chem. A*, 2016, **4**, 3027–3033.
- 95 F. A. Chowdhury, M. L. Trudeau, H. Guo and Z. Mi, *Nat. Commun.*, 2018, **9**, 1707.
- 96 Q. Wang, T. Hisatomi, Q. Jia, H. Tokudome, M. Zhong, C. Wang, Z. Pan, T. Takata, M. Nakabayashi and N. Shibata, *Nat. Mater.*, 2016, **15**, 611–615.
- 97 P. G. Moses and C. G. Van de Walle, *Appl. Phys. Lett.*, 2010, **96**, 021908.
- 98 P. Zhou, I. A. Navid, Y. Ma, Y. Xiao, P. Wang, Z. Ye, B. Zhou, K. Sun and Z. Mi, *Nature*, 2023, **613**, 66–70.
- 99 T. Takata, J. Jiang, Y. Sakata, M. Nakabayashi, N. Shibata, V. Nandal, K. Seki, T. Hisatomi and K. Domen, *Nature*, 2020, **581**, 411–414.
- 100 S. Kim, N. T. Nguyen and C. W. Bark, *Appl. Sci.*, 2018, **8**, 1526.
- 101 M. Sohail, U. Anwar, T. Taha, H. Qazi, A. G. Al-Sehemi, S. Ullah, H. Algarni, I. Ahmed, M. A. Amin and A. Palamanit, *Arabian J. Chem.*, 2022, **15**, 104070.



- 102 J. Sun, D. K. Zhong and D. R. Gamelin, *Energy Environ. Sci.*, 2010, **3**, 1252–1261.
- 103 A. Hayat, M. Sohail, H. Ali, T. Taha, H. Qazi, N. Ur Rahman, Z. Ajmal, A. Kalam, A. G. Al-Sehemi and S. Wageh, *Chem. Rec.*, 2023, **23**, e202200149.
- 104 I. Uddin, H. Ali, A. G. Al-Sehemi, S. Muhammad, N. Hamad, T. Taha, H. S. AlSalem, A. M. Alenad, A. Palamanit and A. Hayat, *S. Afr. J. Bot.*, 2022, **149**, 109–116.
- 105 R. C. Kainthla, B. Zelenay and J. O. M. Bockris, *J. Electrochem. Soc.*, 1987, **134**, 841–845.
- 106 T. Jafari, E. Moharrerri, A. S. Amin, R. Miao, W. Song and S. L. Suib, *Molecules*, 2016, **21**, 900.
- 107 P. Migowski and A. F. Feil, *Recyclable Catal.*, 2016, 1–12.
- 108 X. An, T. Li, B. Wen, J. Tang, Z. Hu, L.-M. Liu, J. Qu, C. P. Huang and H. Liu, *Adv. Energy Mater.*, 2016, **6**, 1502268.
- 109 X. Chen, L. Li, T. Yi, W. Zhang, X. Zhang and L. Wang, *J. Solid State Chem.*, 2015, **229**, 141–149.
- 110 Z. Luo, A. S. Poyraz, C.-H. Kuo, R. Miao, Y. Meng, S.-Y. Chen, T. Jiang, C. Wenos and S. L. Suib, *Chem. Mater.*, 2015, **27**, 6–17.
- 111 V. Nithya, B. Hanitha, S. Surendran, D. Kalpana and R. K. Selvan, *Ultrason. Sonochem.*, 2015, **22**, 300–310.
- 112 J. Yu and X. Yu, *Environ. Sci. Technol.*, 2008, **42**, 4902–4907.
- 113 H. Ahmad, S. K. Kamarudin, L. J. Minggu and M. Kassim, *Renewable Sustainable Energy Rev.*, 2015, **43**, 599–610.
- 114 H. Abbass, *Nanowires – Implementations and Applications*, IntechOpen, 2011.
- 115 A. A. Dubale, C.-J. Pan, A. G. Tamirat, H.-M. Chen, W.-N. Su, C.-H. Chen, J. Rick, D. W. Ayele, B. A. Aragaw, J.-F. Lee, Y.-W. Yang and B.-J. Hwang, *J. Mater. Chem. A*, 2015, **3**, 12482–12499.
- 116 L. Gao, Z. Qiu, W. Gan, X. Zhan, J. Li and T. Qiang, *Sci. Rep.*, 2016, **6**, 26055.
- 117 X. Gao, Z. Wang, F. Fu and W. Li, *Mater. Sci. Semicond. Process.*, 2015, **35**, 197–206.
- 118 F. Li, C. Yang, Q. Li, W. Cao and T. Li, *Mater. Lett.*, 2015, **145**, 52–55.
- 119 N. Guijarro, M. S. Prévot and K. Sivula, *Phys. Chem. Chem. Phys.*, 2015, **17**, 15655–15674.
- 120 N. S. Lewis, *Nature*, 2001, **414**, 589–590.
- 121 S. P. Meshram, P. V. Adhyapak, U. P. Mulik and D. P. Amalnerkar, *Chem. Eng. J.*, 2012, **204–206**, 158–168.
- 122 Y. Lu, H. Shang, F. Shi, C. Chao, X. Zhang and B. Zhang, *J. Phys. Chem. Solids*, 2015, **85**, 44–50.
- 123 W. Liu, G. Zhao, M. An and L. Chang, *Appl. Surf. Sci.*, 2015, **357**, 1053–1063.
- 124 Y. Hu, D. Li, F. Sun, H. Wang, Y. Weng, W. Xiong and Y. Shao, *RSC Adv.*, 2015, **5**, 54882–54889.
- 125 S. Obregón, A. Caballero and G. Colón, *Appl. Catal., B*, 2012, **117–118**, 59–66.
- 126 W. Liu, Y. Yu, L. Cao, G. Su, X. Liu, L. Zhang and Y. Wang, *J. Hazard. Mater.*, 2010, **181**, 1102–1108.
- 127 Y. Guo, X. Yang, F. Ma, K. Li, L. Xu, X. Yuan and Y. Guo, *Appl. Surf. Sci.*, 2010, **256**, 2215–2222.
- 128 Y. Zhao, Y. Xie, X. Zhu, S. Yan and S. Wang, *Chem.–Eur. J.*, 2008, **14**, 1601–1606.
- 129 H. Fan, D. Wang, L. Wang, H. Li, P. Wang, T. Jiang and T. Xie, *Appl. Surf. Sci.*, 2011, **257**, 7758–7762.
- 130 H. Jiang, H. Dai, X. Meng, K. Ji, L. Zhang and J. Deng, *Appl. Catal., B*, 2011, **105**, 326–334.
- 131 Q. Wu, R. Han, P. Chen, X. Qi and W. Yao, *Mater. Sci. Semicond. Process.*, 2015, **38**, 271–277.
- 132 S. Gu, W. Li, F. Wang, S. Wang, H. Zhou and H. Li, *Appl. Catal., B*, 2015, **170–171**, 186–194.
- 133 Z. Guo, P. Li, H. Che, G. Wang, C. Wu, X. Zhang and J. Mu, *Ceram. Int.*, 2016, **42**, 4517–4525.
- 134 P. Ju, Y. Wang, Y. Sun and D. Zhang, *Dalton Trans.*, 2016, **45**, 4588–4602.
- 135 N. Bao, Z. Yin, Q. Zhang, S. He, X. Hu and X. Miao, *Ceram. Int.*, 2016, **42**, 1791–1800.
- 136 X. Zhu, F. Zhang, M. Wang, X. Gao, Y. Luo, J. Xue, Y. Zhang, J. Ding, S. Sun, J. Bao and C. Gao, *Appl. Catal., A*, 2016, **521**, 42–49.
- 137 J. Bao, *Nat. Nanotechnol.*, 2015, **10**, 19–20.
- 138 R. Marschall, *Adv. Funct. Mater.*, 2014, **24**, 2421–2440.
- 139 Y. Wang, Q. Wang, X. Zhan, F. Wang, M. Safdar and J. He, *Nanoscale*, 2013, **5**, 8326–8339.
- 140 J. Li, M. W. G. Hoffmann, H. Shen, C. Fabrega, J. D. Prades, T. Andreu, F. Hernandez-Ramirez and S. Mathur, *J. Mater. Chem.*, 2012, **22**, 20472–20476.
- 141 J. Li, S. K. Cushing, P. Zheng, T. Senty, F. Meng, A. D. Bristow, A. Manivannan and N. Wu, *J. Am. Chem. Soc.*, 2014, **136**, 8438–8449.
- 142 Y. Pihosh, I. Turkevych, K. Mawatari, J. Uemura, Y. Kazoe, S. Kosar, K. Makita, T. Sugaya, T. Matsui, D. Fujita, M. Tosa, M. Kondo and T. Kitamori, *Sci. Rep.*, 2015, **5**, 11141.
- 143 L. Ji, M. D. McDaniel, S. Wang, A. B. Posadas, X. Li, H. Huang, J. C. Lee, A. A. Demkov, A. J. Bard, J. G. Ekerdt and E. T. Yu, *Nat. Nanotechnol.*, 2015, **10**, 84–90.
- 144 K. Zhang, J. Deng, Y. Liu, S. Xie and H. Dai, in *Semiconductor Photocatalysis-Materials, Mechanisms and Applications*, IntechOpen, 2016.
- 145 W. Meng, Z. Wenlong, T. Bin, M. Jiantai and L. Gongxuan, *Appl. Catal., B*, 2018, **236**, 240–252.
- 146 B. Fu, Z. Wu, S. Cao, K. Guo and L. Piao, *Nanoscale*, 2020, **12**, 4895–4902.
- 147 T. Fujiwara, A. Sasahara, N. Hapoo, K. Kimura, K. Hayashi and H. Onishi, *Chem. Mater.*, 2020, **32**, 1439–1447.
- 148 Z. Li, L. Zhang, Y. Liu, C. Shao, Y. Gao, F. Fan, J. Wang, J. Li, J. Yan and R. Li, *Angew. Chem.*, 2020, **132**, 945–952.
- 149 S. Cao, T.-S. Chan, Y.-R. Lu, X. Shi, B. Fu, Z. Wu, H. Li, K. Liu, S. Alzuabi and P. Cheng, *Nano Energy*, 2020, **67**, 104287.
- 150 T. H. Chiang, H. Lyu, T. Hisatomi, Y. Goto, T. Takata, M. Katayama, T. Minegishi and K. Domen, *ACS Catal.*, 2018, **8**, 2782–2788.
- 151 H. Lyu, T. Hisatomi, Y. Goto, M. Yoshida, T. Higashi, M. Katayama, T. Takata, T. Minegishi, H. Nishiyama and T. Yamada, *Chem. Sci.*, 2019, **10**, 3196–3201.
- 152 B. A. Pinaud, J. D. Benck, L. C. Seitz, A. J. Forman, Z. Chen, T. G. Deutsch, B. D. James, K. N. Baum, G. N. Baum and S. Ardo, *Energy Environ. Sci.*, 2013, **6**, 1983–2002.



- 153 T. Hisatomi, J. Kubota and K. Domen, *Chem. Soc. Rev.*, 2014, **43**, 7520–7535.
- 154 S. Cao, L. Piao and X. Chen, *Trends Chem.*, 2020, **2**, 57–70.
- 155 Z. Chai, T.-T. Zeng, Q. Li, L.-Q. Lu, W.-J. Xiao and D. Xu, *J. Am. Chem. Soc.*, 2016, **138**, 10128–10131.
- 156 M. Liu, Y. Chen, J. Su, J. Shi, X. Wang and L. Guo, *Nat. Energy*, 2016, **1**, 1–8.
- 157 T. Su, Z. D. Hood, M. Naguib, L. Bai, S. Luo, C. M. Rouleau, I. N. Ivanov, H. Ji, Z. Qin and Z. Wu, *ACS Appl. Energy Mater.*, 2019, **2**, 4640–4651.
- 158 A. Iwase, S. Nozawa, S.-i. Adachi and A. Kudo, *J. Photochem. Photobiol., A*, 2018, **353**, 284–291.
- 159 J. Zhu, F. Fan, R. Chen, H. An, Z. Feng and C. Li, *Angew. Chem.*, 2015, **127**, 9239–9242.
- 160 Z. Hu, L. Yuan, Z. Liu, Z. Shen and J. C. Yu, *Angew. Chem.*, 2016, **128**, 9732–9737.
- 161 L. Li, X. Mu, W. Liu, Z. Mi and C.-J. Li, *J. Am. Chem. Soc.*, 2015, **137**, 7576–7579.
- 162 S. Cao, J. Jiang, B. Zhu and J. Yu, *Phys. Chem. Chem. Phys.*, 2016, **18**, 19457–19463.
- 163 Z. Wang, C. Li and K. Domen, *Chem. Soc. Rev.*, 2019, **48**, 2109–2125.
- 164 V. B. Y. Oh, S. F. Ng and W. J. Ong, *EcoMat*, 2022, **4**, e12204.
- 165 K. F. Chin, M. Đokić and H. S. Soo, *Trends Chem.*, 2020, **2**, 485–488.
- 166 K. Maeda, K. Teramura, D. Lu, T. Takata, N. Saito, Y. Inoue and K. Domen, *Nature*, 2006, **440**, 295.
- 167 K. Maeda, K. Teramura, H. Masuda, T. Takata, N. Saito, Y. Inoue and K. Domen, *J. Phys. Chem. B*, 2006, **110**, 13107–13112.
- 168 M. Yoshida, K. Takanabe, K. Maeda, A. Ishikawa, J. Kubota, Y. Sakata, Y. Ikezawa and K. Domen, *J. Phys. Chem. C*, 2009, **113**, 10151–10157.
- 169 Z. Li, F. Zhang, J. Han, J. Zhu, M. Li, B. Zhang, W. Fan, J. Lu and C. Li, *Catal. Lett.*, 2018, **148**, 933–939.
- 170 G. Hitoki, A. Ishikawa, T. Takata, J. N. Kondo, M. Hara and K. Domen, *Chem. Lett.*, 2002, **31**, 736–737.
- 171 Z. Wang, Y. Inoue, T. Hisatomi, R. Ishikawa, Q. Wang, T. Takata, S. Chen, N. Shibata, Y. Ikuhara and K. Domen, *Nat. Catal.*, 2018, **1**, 756–763.
- 172 K. Maeda and K. Domen, *J. Phys. Chem. C*, 2007, **111**, 7851–7861.
- 173 C. Pan, T. Takata and K. Domen, *Chem.–Eur. J.*, 2016, **22**, 1854–1862.
- 174 R. Marschall, *Adv. Funct. Mater.*, 2014, **24**, 2421–2440.
- 175 C. M. Wolff, P. D. Frischmann, M. Schulze, B. J. Bohn, R. Wein, P. Livadas, M. T. Carlson, F. Jäckel, J. Feldmann and F. Würthner, *Nat. Energy*, 2018, **3**, 862–869.
- 176 A. Ishikawa, T. Takata, J. N. Kondo, M. Hara, H. Kobayashi and K. Domen, *J. Am. Chem. Soc.*, 2002, **124**, 13547–13553.
- 177 A. Hayat, M. Sohail, M. S. Hamdy, T. Taha, H. S. AlSalem, A. M. Alenad, M. A. Amin, R. Shah, A. Palamanit and J. Khan, *Surf. Interfaces*, 2022, **29**, 101725.
- 178 W. Zhao, K. Maeda, F. Zhang, T. Hisatomi and K. Domen, *Phys. Chem. Chem. Phys.*, 2014, **16**, 12051–12056.
- 179 G. Ma, Y. Kuang, D. H. Murthy, T. Hisatomi, J. Seo, S. Chen, H. Matsuzaki, Y. Suzuki, M. Katayama and T. Minegishi, *J. Phys. Chem. C*, 2018, **122**, 13492–13499.
- 180 Q. Wang, M. Nakabayashi, T. Hisatomi, S. Sun, S. Akiyama, Z. Wang, Z. Pan, X. Xiao, T. Watanabe and T. Yamada, *Nat. Mater.*, 2019, **18**, 827–832.
- 181 X. Wang, K. Maeda, A. Thomas, K. Takanabe, G. Xin, J. M. Carlsson, K. Domen and M. Antonietti, *Nat. Mater.*, 2009, **8**, 76–80.
- 182 Y. Zheng, L. Lin, B. Wang and X. Wang, *Angew. Chem., Int. Ed.*, 2015, **54**, 12868–12884.
- 183 W.-J. Ong, L.-L. Tan, Y. H. Ng, S.-T. Yong and S.-P. Chai, *Chem. Rev.*, 2016, **116**, 7159–7329.
- 184 G. Zhang, Z.-A. Lan, L. Lin, S. Lin and X. Wang, *Chem. Sci.*, 2016, **7**, 3062–3066.
- 185 Z. Pan, Y. Zheng, F. Guo, P. Niu and X. Wang, *ChemSusChem*, 2017, **10**, 87–90.
- 186 L. Lin, C. Wang, W. Ren, H. Ou, Y. Zhang and X. Wang, *Chem. Sci.*, 2017, **8**, 5506–5511.
- 187 L. Wang, Y. Wan, Y. Ding, S. Wu, Y. Zhang, X. Zhang, G. Zhang, Y. Xiong, X. Wu and J. Yang, *Adv. Mater.*, 2017, **29**, 1702428.
- 188 L. Lin, Z. Yu and X. Wang, *Angew. Chem.*, 2019, **131**, 6225–6236.
- 189 K. Maeda, *ACS Catal.*, 2013, **3**, 1486–1503.
- 190 K. Sayama, K. Mukasa, R. Abe, Y. Abe and H. Arakawa, *J. Photochem. Photobiol., A*, 2002, **148**, 71–77.
- 191 Q. Jia, A. Iwase and A. Kudo, *Chem. Sci.*, 2014, **5**, 1513–1519.
- 192 Y. Qi, S. Chen, M. Li, Q. Ding, Z. Li, J. Cui, B. Dong, F. Zhang and C. Li, *Chem. Sci.*, 2017, **8**, 437–443.
- 193 K. Maeda, M. Higashi, D. Lu, R. Abe and K. Domen, *J. Am. Chem. Soc.*, 2010, **132**, 5858–5868.
- 194 S. Chen, Y. Qi, T. Hisatomi, Q. Ding, T. Asai, Z. Li, S. S. K. Ma, F. Zhang, K. Domen and C. Li, *Angew. Chem.*, 2015, **127**, 8618–8621.
- 195 Z. Song, T. Hisatomi, S. Chen, Q. Wang, G. Ma, S. Li, X. Zhu, S. Sun and K. Domen, *ChemSusChem*, 2019, **12**, 1906–1910.
- 196 T. Oshima, S. Nishioka, Y. Kikuchi, S. Hirai, K.-i. Yanagisawa, M. Eguchi, Y. Miseki, T. Yokoi, T. Yui and K. Kimoto, *J. Am. Chem. Soc.*, 2020, **142**, 8412–8420.
- 197 H. Fujito, H. Kunioku, D. Kato, H. Suzuki, M. Higashi, H. Kageyama and R. Abe, *J. Am. Chem. Soc.*, 2016, **138**, 2082–2085.
- 198 Y. Qi, Y. Zhao, Y. Gao, D. Li, Z. Li, F. Zhang and C. Li, *Joule*, 2018, **2**, 2393–2402.
- 199 Y. Miseki, H. Kusama and K. Sayama, *Chem. Lett.*, 2012, **41**, 1489–1491.
- 200 Y. Miseki, H. Kusama, H. Sugihara and K. Sayama, *J. Phys. Chem. Lett.*, 2010, **1**, 1196–1200.
- 201 Y. Miseki and K. Sayama, *Chem. Commun.*, 2018, **54**, 2670–2673.
- 202 A. Iwase, S. Yoshino, T. Takayama, Y. H. Ng, R. Amal and A. Kudo, *J. Am. Chem. Soc.*, 2016, **138**, 10260–10264.
- 203 Z. Pan, G. Zhang and X. Wang, *Angew. Chem.*, 2019, **131**, 7176–7180.
- 204 M. Sohail, H. Xue, Q. Jiao, H. Li, K. Khan, S. Wang and Y. Zhao, *Mater. Res. Bull.*, 2017, **90**, 125–130.



- 205 M. Sohail, H. Xue, Q. Jiao, H. Li, K. Khan, S. Wang, C. Feng and Y. Zhao, *Mater. Res. Bull.*, 2018, **101**, 83–89.
- 206 J. Hu, H. Li, S. Muhammad, Q. Wu, Y. Zhao and Q. Jiao, *J. Solid State Chem.*, 2017, **253**, 113–120.
- 207 L. Wang, X. Zheng, L. Chen, Y. Xiong and H. Xu, *Angew. Chem., Int. Ed.*, 2018, **57**, 3454–3458.
- 208 R. Asahi, T. Morikawa, T. Ohwaki, K. Aoki and Y. Taga, *Science*, 2001, **293**, 269–271.
- 209 X. Chen, L. Liu, P. Y. Yu and S. S. Mao, *Science*, 2011, **331**, 746–750.
- 210 N. Liu, V. Haublein, X. Zhou, U. Venkatesan, M. Hartmann, M. Mackovic, T. Nakajima, E. Spiecker, A. Osvet and L. Frey, *Nano Lett.*, 2015, **15**, 6815–6820.
- 211 W. Choi, A. Termin and M. R. Hoffmann, *J. Phys. Chem.*, 2002, **98**, 13669–13679.
- 212 R. Asahi, T. Morikawa, H. Irie and T. Ohwaki, *Chem. Rev.*, 2014, **114**, 9824–9852.
- 213 I. Ullah, T. Taha, A. M. Alenad, I. Uddin, A. Hayat, A. Hayat, M. Sohail, A. Irfan, J. Khan and A. Palamanit, *Surf. Interfaces*, 2021, **25**, 101227.
- 214 S. A. Ansari, M. M. Khan, M. O. Ansari and M. H. Cho, *New J. Chem.*, 2016, **40**, 3000–3009.
- 215 S. Sato, *Chem. Phys. Lett.*, 1986, **123**, 126–128.
- 216 A. Hayat, M. Sohail, T. Taha, A. M. Alenad, I. Uddin, A. Hayat, T. Ali, R. Shah, A. Irfan and W. U. Khan, *Catalysts*, 2021, **11**, 935.
- 217 S. Livraghi, M. C. Paganini, E. Giamello, A. Selloni, C. Di Valentin and G. Pacchioni, *J. Am. Chem. Soc.*, 2006, **128**, 15666–15671.
- 218 C. Di Valentin, G. Pacchioni, A. Selloni, S. Livraghi and E. Giamello, *J. Phys. Chem. B*, 2005, **109**, 11414–11419.
- 219 G. Wang, H. Wang, Y. Ling, Y. Tang, X. Yang, R. C. Fitzmorris, C. Wang, J. Z. Zhang and Y. Li, *Nano Lett.*, 2011, **11**, 3026–3033.
- 220 A. J. Cowan, J. Tang, W. Leng, J. R. Durrant and D. R. Klug, *J. Phys. Chem. C*, 2010, **114**, 4208–4214.
- 221 A. Imanishi, T. Okamura, N. Ohashi, R. Nakamura and Y. Nakato, *J. Am. Chem. Soc.*, 2007, **129**, 11569–11578.
- 222 A. Padilha, H. Raebiger, A. Rocha and G. Dalpian, *Sci. Rep.*, 2016, **6**, 28871.
- 223 J. Li, L. Cai, J. Shang, Y. Yu and L. Zhang, *Adv. Mater.*, 2016, **28**, 4059–4064.
- 224 R. Asai, H. Nemoto, Q. Jia, K. Saito, A. Iwase and A. Kudo, *Chem. Commun.*, 2014, **50**, 2543–2546.
- 225 W. J. Jo, H. J. Kang, K.-J. Kong, Y. S. Lee, H. Park, Y. Lee, T. Buonassisi, K. K. Gleason and J. S. Lee, *Proc. Natl. Acad. Sci. U. S. A.*, 2015, **112**, 13774–13778.
- 226 R. Li, F. Zhang, D. Wang, J. Yang, M. Li, J. Zhu, X. Zhou, H. Han and C. Li, *Nat. Commun.*, 2013, **4**, 1432.
- 227 L. Li, J. Yan, T. Wang, Z.-J. Zhao, J. Zhang, J. Gong and N. Guan, *Nat. Commun.*, 2015, **6**, 5881.
- 228 G. Liu, H. G. Yang, J. Pan, Y. Q. Yang, G. Q. Lu and H.-M. Cheng, *Chem. Rev.*, 2014, **114**, 9559–9612.
- 229 Y.-C. Zhang, Z. Li, L. Zhang, L. Pan, X. Zhang, L. Wang and J.-J. Zou, *Appl. Catal., B*, 2018, **224**, 101–108.
- 230 M. Long and L. Zheng, *Chin. J. Catal.*, 2017, **38**, 617–624.
- 231 K. Maeda, K. Teramura, D. Lu, N. Saito, Y. Inoue and K. Domen, *Angew. Chem.*, 2006, **118**, 7970–7973.
- 232 F. Esch, S. Fabris, L. Zhou, T. Montini, C. Africh, P. Fornasiero, G. Comelli and R. Rosei, *Science*, 2005, **309**, 752–755.
- 233 Y. Li, Y.-K. Peng, L. Hu, J. Zheng, D. Prabhakaran, S. Wu, T. J. Puchtler, M. Li, K.-Y. Wong, R. A. Taylor and S. C. E. Tsang, *Nat. Commun.*, 2019, **10**, 4421.
- 234 I. Nakamura, N. Negishi, S. Kutsuna, T. Ihara, S. Sugihara and K. Takeuchi, *J. Mol. Catal. A: Chem.*, 2000, **161**, 205–212.
- 235 H. Tan, Z. Zhao, M. Niu, C. Mao, D. Cao, D. Cheng, P. Feng and Z. Sun, *Nanoscale*, 2014, **6**, 10216–10223.
- 236 H. Tan, Z. Zhao, W.-b. Zhu, E. N. Coker, B. Li, M. Zheng, W. Yu, H. Fan and Z. Sun, *ACS Appl. Mater. Interfaces*, 2014, **6**, 19184–19190.
- 237 J. Wang, D. N. Tafen, J. P. Lewis, Z. Hong, A. Manivannan, M. Zhi, M. Li and N. Wu, *J. Am. Chem. Soc.*, 2009, **131**, 12290–12297.
- 238 Z. Su, F. Fang, X. Li, W. Han, X. Liu and K. Chang, *J. Colloid Interface Sci.*, 2022, **626**, 662–673.
- 239 A. Hayat, M. Sohail, T. A. M. Taha, A. M. Alenad, M. A. Amin, A. Hayat, A. Irfan, A. Palamanit, Y. Al-Hadeethi and S. K. B. Mane, *Int. J. Energy Res.*, 2022, **46**, 1882–1893.
- 240 T. Takata, C. Pan, M. Nakabayashi, N. Shibata and K. Domen, *J. Am. Chem. Soc.*, 2015, **137**, 9627–9634.
- 241 K. Maeda, K. Teramura, D. Lu, N. Saito, Y. Inoue and K. Domen, *Angew. Chem.*, 2006, **118**, 7970–7973.
- 242 J. Liu, Y. Liu, N. Liu, Y. Han, X. Zhang, H. Huang, Y. Lifshitz, S.-T. Lee, J. Zhong and Z. Kang, *Science*, 2015, **347**, 970–974.
- 243 C. J. Shearer, J. F. Alvino, M. Batmunkh and G. F. Metha, *C*, 2018, **4**, 64.
- 244 H. Su, W. Che, F. Tang, W. Cheng, X. Zhao, H. Zhang and Q. Liu, *J. Phys. Chem. C*, 2018, **122**, 21108–21114.
- 245 Q. Zhao, W. Yao, C. Huang, Q. Wu and Q. Xu, *ACS Appl. Mater. Interfaces*, 2017, **9**, 42734–42741.
- 246 M. Karakus, Y. Sung, H. I. Wang, Z. n. Mics, K. Char, M. Bonn and E. Cánovas, *J. Phys. Chem. C*, 2017, **121**, 13070–13077.
- 247 A. Tanaka, K. Teramura, S. Hosokawa, H. Kominami and T. Tanaka, *Chem. Sci.*, 2017, **8**, 2574–2580.
- 248 D. Wang, Z.-P. Liu and W.-M. Yang, *ACS Catal.*, 2018, **8**, 7270–7278.
- 249 W. Kurashige, R. Kumazawa, Y. Mori and Y. Negishi, *J. Mater. Appl.*, 2018, **7**, 1–11.
- 250 S. Pokrant, S. Dilger, S. Landsmann and M. Trottmann, *Mater. Today Energy*, 2017, **5**, 158–163.
- 251 M. Luo, P. Lu, W. Yao, C. Huang, Q. Xu, Q. Wu, Y. Kuwahara and H. Yamashita, *ACS Appl. Mater. Interfaces*, 2016, **8**, 20667–20674.
- 252 L. Yin, X. Hai, K. Chang, F. Ichihara and J. Ye, *Small*, 2018, **14**, 1704153.
- 253 J. Fu, C. Bie, B. Cheng, C. Jiang and J. Yu, *ACS Sustainable Chem. Eng.*, 2018, **6**, 2767–2779.
- 254 Z. Sun, B. Lv, J. Li, M. Xiao, X. Wang and P. Du, *J. Mater. Chem. A*, 2016, **4**, 1598–1602.



- 255 C. Ding, J. Shi, Z. Wang and C. Li, *ACS Catal.*, 2017, **7**, 675–688.
- 256 T. Yoshinaga, M. Saruyama, A. Xiong, Y. Ham, Y. Kuang, R. Niishiro, S. Akiyama, M. Sakamoto, T. Hisatomi and K. Domen, *Nanoscale*, 2018, **10**, 10420–10427.
- 257 A. Hayat, M. Sohail, M. S. Hamdy, S. K. B. Mane, M. A. Amin, A. Zada, T. Taha, M. M. Rahman, A. Palamanit and D. Medina, *Mol. Catal.*, 2022, **518**, 112064.
- 258 B. Han and Y. H. Hu, *J. Phys. Chem. C*, 2015, **119**, 18927–18934.
- 259 B. Tian, B. Tian, B. Smith, M. Scott, R. Hua, Q. Lei and Y. Tian, *Nat. Commun.*, 2018, **9**, 1397.
- 260 B. Wang, B. An, X. Li and S. Shen, *Front. Energy*, 2023, 1–9.
- 261 B. Tian, B. Tian, B. Smith, M. Scott, R. Hua, Q. Lei and Y. Tian, *Nat. Commun.*, 2018, **9**, 1397.
- 262 A. V. Bandura and S. N. Lvov, *J. Phys. Chem. Ref. Data*, 2006, **35**, 15–30.
- 263 Y.-K. Peng and S. E. Tsang, *Nano Today*, 2018, **18**, 15–34.
- 264 F. Chen, H. Huang, L. Guo, Y. Zhang and T. Ma, *Angew. Chem., Int. Ed.*, 2019, **58**, 10061–10073.
- 265 J. Li, G. Zhan, Y. Yu and L. Zhang, *Nat. Commun.*, 2016, **7**, 11480.
- 266 J. Li, L. Cai, J. Shang, Y. Yu and L. Zhang, *Adv. Mater.*, 2016, **28**, 4059–4064.
- 267 C. Noguera, *J. Phys.: Condens. Matter*, 2000, **12**, R367.
- 268 V. Kumaravel, M. D. Imam, A. Badreldin, R. K. Chava, J. Y. Do, M. Kang and A. Abdel-Wahab, *Catalysts*, 2019, **9**, 276.
- 269 M. Ni, M. K. Leung, D. Y. Leung and K. Sumathy, *Renewable Sustainable Energy Rev.*, 2007, **11**, 401–425.
- 270 A. Galińska and J. Walendziewski, *Energy Fuels*, 2005, **19**, 1143–1147.
- 271 A. Kudo, H. Kato and I. Tsuji, *Chem. Lett.*, 2004, **33**, 1534–1539.
- 272 A. Hayat, M. Sohail, J. Ali Shah Syed, A. G. Al-Sehemi, M. H. Mohammed, A. A. Al-Ghamdi, T. Taha, H. Salem ALSalem, A. M. Alenad and M. A. Amin, *Chem. Rec.*, 2022, **22**, e202100310.
- 273 X. Zong, G. Wu, H. Yan, G. Ma, J. Shi, F. Wen, L. Wang and C. Li, *J. Phys. Chem. C*, 2010, **114**, 1963–1968.
- 274 N. Bao, L. Shen, T. Takata and K. Domen, *Chem. Mater.*, 2008, **20**, 110–117.
- 275 M. R. Gholipour, C.-T. Dinh, F. Bédard and T.-O. Do, *Nanoscale*, 2015, **7**, 8187–8208.
- 276 F. Guzman, S. S. Chuang and C. Yang, *Ind. Eng. Chem. Res.*, 2013, **52**, 61–65.
- 277 J. Wang, P. Yang, B. Cao, J. Zhao and Z. Zhu, *Appl. Surf. Sci.*, 2015, **325**, 86–90.
- 278 B. Ma, F. Wen, H. Jiang, J. Yang, P. Ying and C. Li, *Catal. Lett.*, 2010, **134**, 78–86.
- 279 T. Wei, P. Ding, T. Wang, L.-M. Liu, X. An and X. Yu, *ACS Catal.*, 2021, **11**, 14669–14676.
- 280 Z. Liang, R. Shen, Y. H. Ng, P. Zhang, Q. Xiang and X. Li, *J. Mater. Sci. Technol.*, 2020, **56**, 89–121.
- 281 C. Ma, J. Lee, Y. Kim, W. C. Seo, H. Jung and W. Yang, *J. Colloid Interface Sci.*, 2021, **581**, 514–522.
- 282 J. Yang, Y. Liang, K. Li, G. Yang, K. Wang, R. Xu and X. Xie, *Appl. Catal., B*, 2020, **262**, 118252.
- 283 F. Vaquero, R. Navarro and J. Fierro, *Appl. Catal., B*, 2017, **203**, 753–767.
- 284 C. Cheng, L. Mao, J. Shi, F. Xue, S. Zong, B. Zheng and L. Guo, *J. Mater. Chem. A*, 2021, **9**, 2299–12306.
- 285 J. Kosco, M. Bidwell, H. Cha, T. Martin, C. T. Howells, M. Sachs, D. H. Anjum, S. Gonzalez Lopez, L. Zou and A. Wadsworth, *Nat. Mater.*, 2020, **19**, 559–565.
- 286 J. Zhang, H. Gu, X. Wang, H. Zhang, L. Li, X. Wang and W.-L. Dai, *Catal. Sci. Technol.*, 2022, **12**, 2346–2359.
- 287 W. Hu, W. Zhou, K. Zhang, X. Zhang, L. Wang, B. Jiang, G. Tian, D. Zhao and H. Fu, *J. Mater. Chem. A*, 2016, **4**, 7495–7502.
- 288 W. Zhou, W. Li, J.-Q. Wang, Y. Qu, Y. Yang, Y. Xie, K. Zhang, L. Wang, H. Fu and D. Zhao, *J. Am. Chem. Soc.*, 2014, **136**, 9280–9283.
- 289 J. Wei, Y. Chen, H. Zhang, Z. Zhuang and Y. Yu, *Chin. J. Catal.*, 2021, **42**, 78–86.
- 290 S. Mao, J.-W. Shi, G. Sun, D. Ma, C. He, Z. Pu, K. Song and Y. Cheng, *Appl. Catal., B*, 2021, **282**, 119550.
- 291 D. Luo, L. Peng, Y. Wang, X. Lu, C. Yang, X. Xu, Y. Huang and Y. Ni, *J. Mater. Chem. A*, 2021, **9**, 908–914.
- 292 T. Shen, X. Shi, J. Guo, J. Li and S. Yuan, *Chem. Eng. J.*, 2021, **408**, 128014.
- 293 T. Jia, J. Wu, Z. Ji, C. Peng, Q. Liu, M. Shi, J. Zhu, H. Wang, D. Liu and M. Zhou, *Appl. Catal., B*, 2021, **284**, 119727.
- 294 K. Wang, S. Liu, Y. Li, G. Wang, M. Yang and Z. Jin, *Appl. Surf. Sci.*, 2022, **601**, 154174.
- 295 Y. Zhu, T. Wan, X. Wen, D. Chu and Y. Jiang, *Appl. Catal., B*, 2019, **244**, 814–822.
- 296 G. Li, Y. Cai, X. Wang, L. Zhang, Q. Xie, P. Chen, C. Li, J. Sun, T. Li and L. Dong, *Chem. Phys.*, 2022, **559**, 111558.
- 297 C. Yang, D. Bu and S. Huang, *Chem. Eng. J.*, 2022, **446**, 137026.
- 298 C. Ding, J. Guo, P. Chen, W. Gan, Z. Yin, S. Qi, M. Zhang and Z. Sun, *Appl. Surf. Sci.*, 2022, **596**, 153629.
- 299 Z. Hu, D. Shi, G. Wang, T. Gao, J. Wang, L. Lu and J. Li, *Appl. Surf. Sci.*, 2022, **601**, 154167.
- 300 Q. Xu, L. Zhang, B. Cheng, J. Fan and J. Yu, *Chem*, 2020, **6**, 1543–1559.
- 301 S. Meng, C. Chen, X. Gu, H. Wu, Q. Meng, J. Zhang, S. Chen, X. Fu, D. Liu and W. Lei, *Appl. Catal., B*, 2021, **285**, 119789.
- 302 D. Zheng, Y. Xue, J. Wang, P. S. Varbanov, J. J. Klemeš and C. Yin, *J. Cleaner Prod.*, 2023, 137700.
- 303 Q. Hu, G. Li, H. Lan, J. Li, B. Hu, W. Guo, J. Huang and X. Huang, *Cryst. Growth Des.*, 2019, **19**, 1680–1688.
- 304 J. S. Chen, Y. L. Tan, C. M. Li, Y. L. Cheah, D. Luan, S. Madhavi, F. Y. C. Boey, L. A. Archer and X. W. Lou, *J. Am. Chem. Soc.*, 2010, **132**, 6124–6130.
- 305 S. Mukhopadhyay, D. Maiti, A. Saha and P. S. Devi, *Cryst. Growth Des.*, 2016, **16**, 6922–6932.
- 306 F. Fang, F. Xu, Z. Su, X. Li, W. Han, Y. Qin, J. Ye and K. Chang, *Appl. Catal., B*, 2022, **316**, 121613.
- 307 L. Liu, Z. Liu, A. Liu, X. Gu, C. Ge, F. Gao and L. Dong, *ChemSusChem*, 2014, **7**, 618–626.



- 308 N. Khakpash, A. Simchi and T. Jafari, *J. Mater. Sci.: Mater. Electron.*, 2012, **23**, 659–667.
- 309 S. Wang, L. Pan, J.-J. Song, W. Mi, J.-J. Zou, L. Wang and X. Zhang, *J. Am. Chem. Soc.*, 2015, **137**, 2975–2983.
- 310 R. Miao, Z. Luo, W. Zhong, S.-Y. Chen, T. Jiang, B. Dutta, Y. Nasr, Y. Zhang and S. L. Suib, *Appl. Catal., B*, 2016, **189**, 26–38.
- 311 E. Pulido Melián, O. González Díaz, A. Ortega Méndez, C. R. López, M. Nereida Suárez, J. M. Doña Rodríguez, J. A. Navío, D. Fernández Hevia and J. Pérez Peña, *Int. J. Hydrogen Energy*, 2013, **38**, 2144–2155.
- 312 X. Chen and S. S. Mao, *Chem. Rev.*, 2007, **107**, 2891–2959.
- 313 J. Tang, A. J. Cowan, J. R. Durrant and D. R. Klug, *J. Phys. Chem. C*, 2011, **115**, 3143–3150.
- 314 S. Piskunov, O. Lisovski, J. Begens, D. Bocharov, Y. F. Zhukovskii, M. Wessel and E. Spohr, *J. Phys. Chem. C*, 2015, **119**, 18686–18696.
- 315 H. Luo, T. Takata, Y. Lee, J. Zhao, K. Domen and Yan, *Chem. Mater.*, 2004, **16**, 846–849.
- 316 H. Wang, S. Dong, Y. Chang and J. L. Faria, *J. Hazard. Mater.*, 2012, **235–236**, 230–236.
- 317 Z. Li, B. Gao, G. Z. Chen, R. Mokaya, S. Sotiropoulos and G. Li Puma, *Appl. Catal., B*, 2011, **110**, 50–57.
- 318 Y.-J. Xu, Y. Zhuang and X. Fu, *J. Phys. Chem. C*, 2010, **114**, 2669–2676.
- 319 V. J. Babu, S. Vempati, T. Uyar and S. Ramakrishna, *Phys. Chem. Chem. Phys.*, 2015, **17**, 2960–2986.
- 320 X. Chen, S. Shen, L. Guo and S. S. Mao, *Chem. Rev.*, 2010, **110**, 6503–6570.
- 321 J. Resasco, H. Zhang, N. Kornienko, N. Becknell, H. Lee, J. Guo, A. L. Briseno and P. Yang, *ACS Cent. Sci.*, 2016, **2**, 80–88.
- 322 W.-T. Chen, A. Chan, Z. H. N. Al-Azri, A. G. Dosado, M. A. Nadeem, D. Sun-Waterhouse, H. Idriss and G. I. N. Waterhouse, *J. Catal.*, 2015, **329**, 499–513.
- 323 M. Reza Gholipour, C.-T. Dinh, F. Bèland and T.-O. Do, *Nanoscale*, 2015, **7**, 8187–8208.
- 324 I. Majeed, M. A. Nadeem, M. Al-Oufi, M. A. Nadeem, G. I. N. Waterhouse, A. Badshah, J. B. Metson and H. Idriss, *Appl. Catal., B*, 2016, **182**, 266–276.
- 325 Y. Tian and T. Tatsuma, *J. Am. Chem. Soc.*, 2005, **127**, 7632–7637.
- 326 K. C. Ko, S. T. Bromley, J. Y. Lee and F. Illas, *J. Phys. Chem. Lett.*, 2017, **8**, 5593–5598.
- 327 B. Wu, D. Liu, S. Mubeen, T. T. Chuong, M. Moskovits and G. D. Stucky, *J. Am. Chem. Soc.*, 2016, **138**, 1114–1117.
- 328 S. Xie, Q. Zhang, G. Liu and Y. Wang, *Chem. Commun.*, 2016, **52**, 35–59.
- 329 J. Huo, Y. Hu, H. Jiang and C. Li, *Nanoscale*, 2014, **6**, 9078–9084.
- 330 V. J. Babu, S. Vempati, T. Uyar and S. Ramakrishna, *Phys. Chem. Chem. Phys.*, 2015, **17**, 2960–2986.
- 331 H. Lüth and G. Heiland, *Phys. Status Solidi A*, 1972, **14**, 573–577.
- 332 A. Walsh, Y. Yan, M. N. Huda, M. M. Al-Jassim and S.-H. Wei, *Chem. Mater.*, 2009, **21**, 547–551.
- 333 Z. Ajmal, A. Muhmood, R. Dong and S. Wu, *J. Environ. Manage.*, 2020, **253**, 109730.
- 334 Z. Ajmal, A. Muhmood, M. Usman, S. Kizito, J. Lu, R. Dong and S. Wu, *J. Colloid Interface Sci.*, 2018, **528**, 145–155.
- 335 Z. Ajmal, M. Usman, I. Anastopoulos, A. Qadeer, R. Zhu, A. Wakeel and R. Dong, *J. Environ. Manage.*, 2020, **264**, 110477.
- 336 K. J. Kim and Y. R. Park, *Solid State Commun.*, 2003, **127**, 25–28.
- 337 A. Walsh and G. W. Watson, *J. Solid State Chem.*, 2005, **178**, 1422–1428.
- 338 L. Kong, H. Chen, W. Hua, S. Zhang and J. Chen, *Chem. Commun.*, 2008, 4977–4979, DOI: [10.1039/B808911F](https://doi.org/10.1039/B808911F).
- 339 Y. Hosogi, Y. Shimodaira, H. Kato, H. Kobayashi and A. Kudo, *Chem. Mater.*, 2008, **20**, 1299–1307.
- 340 K. Sayama, A. Nomura, T. Arai, T. Sugita, R. Abe, M. Yanagida, T. Oi, Y. Iwasaki, Y. Abe and H. Sugihara, *J. Phys. Chem. B*, 2006, **110**, 11352–11360.
- 341 K. Sayama, A. Nomura, Z. Zou, R. Abe, Y. Abe and H. Arakawa, *Chem. Commun.*, 2003, 2908–2909, DOI: [10.1039/B310428A](https://doi.org/10.1039/B310428A).
- 342 M. Mishra and D.-M. Chun, *Appl. Catal., A*, 2015, **498**, 126–141.
- 343 S. Haghghat and J. M. Dawlaty, *J. Phys. Chem. C*, 2015, **119**, 6619–6625.
- 344 C. G. Morales-Guio, M. T. Mayer, A. Yella, S. D. Tilley, M. Grätzel and X. Hu, *J. Am. Chem. Soc.*, 2015, **137**, 9927–9936.
- 345 V. Dutta, S. Sharma, P. Raizada, V. K. Thakur, A. A. P. Khan, V. Saini, A. M. Asiri and P. Singh, *J. Environ. Chem. Eng.*, 2021, **9**, 105018.
- 346 A. W. Amer, M. A. El-Sayed and N. K. Allam, *J. Phys. Chem. C*, 2016, **120**, 7025–7032.
- 347 G. S. Costa, M. Costa, H. Oliveira, L. Lima, G. Luz, L. Cavalcante and R. Santos, *J. Inorg. Organomet. Polym. Mater.*, 2020, **30**, 2851–2862.
- 348 L. Liao, Q. Zhang, Z. Su, Z. Zhao, Y. Wang, Y. Li, X. Lu, D. Wei, G. Feng, Q. Yu, X. Cai, J. Zhao, Z. Ren, H. Fang, F. Robles-Hernandez, S. Baldelli and J. Bao, *Nat. Nanotechnol.*, 2014, **9**, 69–73.
- 349 X. Zhan, Z. Wang, F. Wang, Z. Cheng, K. Xu, Q. Wang, M. Safdar and J. He, *Appl. Phys. Lett.*, 2014, **105**, 153903.
- 350 J. H. Baek, B. J. Kim, G. S. Han, S. W. Hwang, D. R. Kim, I. S. Cho and H. S. Jung, *ACS Appl. Mater. Interfaces*, 2017, **9**, 1479–1487.
- 351 A. A. Ismail and D. W. Bahnemann, *Sol. Energy Mater. Sol. Cells*, 2014, **128**, 85–101.
- 352 J. Cao, J. Z. Sun, J. Hong, H. Y. Li, H. Z. Chen and M. Wang, *Adv. Mater.*, 2004, **16**, 84–87.
- 353 Z. F. Huang, J. Song, K. Li, M. Tahir, Y. T. Wang, L. Pan, L. Wang, X. Zhang and J. J. Zou, *J. Am. Chem. Soc.*, 2016, **138**, 1359–1365.
- 354 J. Ran, J. Zhang, J. Yu, M. Jaroniec and S. Z. Qiao, *Chem. Soc. Rev.*, 2014, **43**, 7787–7812.
- 355 S. Yu, J. Hu and J. Li, *Int. J. Photoenergy*, 2014, **2014**, 854217.
- 356 Q. Li, H. Meng, P. Zhou, Y. Zheng, J. Wang, J. Yu and J. Gong, *ACS Catal.*, 2013, **3**, 882–889.



- 357 Y. X. Pan, H. Zhuang, J. Hong, Z. Fang, H. Liu, B. Liu, Y. Huang and R. Xu, *ChemSusChem*, 2014, **7**, 2537–2544.
- 358 X. Wang, G. Liu, G. Q. Lu and H.-M. Cheng, *Int. J. Hydrogen Energy*, 2010, **35**, 8199–8205.
- 359 J. Hou, Z. Wang, W. Kan, S. Jiao, H. Zhu and R. V. Kumar, *J. Mater. Chem.*, 2012, **22**, 7291–7299.
- 360 S. Bai and X. Shen, *RSC Adv.*, 2012, **2**, 64–98.
- 361 Z. Cheng, Z. Wang, T. A. Shifa, F. Wang, X. Zhan, K. Xu, Q. Liu and J. He, *Appl. Phys. Lett.*, 2015, **107**, 223902.
- 362 H. Kato, K. Asakura and A. Kudo, *J. Am. Chem. Soc.*, 2003, **125**, 3082–3089.
- 363 K. Maeda, T. Takata, M. Hara, N. Saito, Y. Inoue, H. Kobayashi and K. Domen, *J. Am. Chem. Soc.*, 2005, **127**, 8286–8287.
- 364 K. Maeda, K. Teramura and K. Domen, *J. Catal.*, 2008, **254**, 198–204.
- 365 J. Kubota and K. Domen, *Interface Mag.*, 2013, **22**, 57–62.
- 366 C. Zhen, L. Wang, G. Liu, G. Q. Lu and H.-M. Cheng, *Chem. Commun.*, 2013, **49**, 3019–3021.
- 367 J. Seo, T. Takata, M. Nakabayashi, T. Hisatomi, N. Shibata, T. Minegishi and K. Domen, *J. Am. Chem. Soc.*, 2015, **137**, 12780–12783.
- 368 X. Wang, K. Maeda, A. Thomas, K. Takanabe, G. Xin, J. M. Carlsson, K. Domen and M. Antonietti, *Nat. Mater.*, 2009, **8**, 76–80.
- 369 G. Zhang, M. Zhang, X. Ye, X. Qiu, S. Lin and X. Wang, *Adv. Mater.*, 2014, **26**, 805–809.
- 370 Z. Ding, X. Chen, M. Antonietti and X. Wang, *ChemSusChem*, 2011, **4**, 274–281.
- 371 A. Hayat, M. U. Rahman, I. Khan, J. Khan, M. Sohail, H. Yasmeen, S.-y. Liu, K. Qi and W. Lv, *Molecules*, 2019, **24**, 1779.
- 372 A. Hayat, J. Khan, M. U. Rahman, S. B. Mane, W. U. Khan, M. Sohail, N. U. Rahman, N. Shaishita, Z. Chi and M. Wu, *J. Colloid Interface Sci.*, 2019, **548**, 197–205.
- 373 A. Hayat, J. A. S. Syed, A. G. Al-Sehemi, K. S. El-Nasser, T. Taha, A. A. Al-Ghamdi, M. A. Amin, Z. Ajmal, W. Iqbal and A. Palamanit, *Int. J. Hydrogen Energy*, 2022, **47**, 10837–10867.
- 374 A. Ullah, J. Khan, M. Sohail, A. Hayat, T. K. Zhao, B. Ullah, M. Khan, I. Uddin, S. Ullah and R. Ullah, *J. Photochem. Photobiol., A*, 2020, **401**, 112764.
- 375 J. Zhang, Y. Chen and X. Wang, *Energy Environ. Sci.*, 2015, **8**, 3092–3108.
- 376 M. Sumathi, A. Prakasam and P. M. Anbarasan, *J. Mater. Sci.: Mater. Electron.*, 2019, **30**, 3294–3304.
- 377 X. C. Wu, Y. R. Tao, L. Li, Y. Bando and D. Golberg, *Nanotechnology*, 2013, **24**, 175701.
- 378 M. Naguib, M. Kurtoglu, V. Presser, J. Lu, J. Niu, M. Heon, L. Hultman, Y. Gogotsi and M. W. Barsoum, *Adv. Mater.*, 2011, **23**, 4248–4253.
- 379 J. Fu, J. Yu, C. Jiang and B. Cheng, *Adv. Energy Mater.*, 2018, **8**, 1701503.
- 380 Y. Li, X. Wang, J. Gong, Y. Xie, X. Wu and G. Zhang, *ACS Appl. Mater. Interfaces*, 2018, **10**, 43760–43767.
- 381 L. Jiang, K. Wang, X. Wu, G. Zhang and S. Yin, *ACS Appl. Mater. Interfaces*, 2019, **11**, 26898–26908.
- 382 L. Cheng, X. Li, H. Zhang and Q. Xiang, *J. Phys. Chem. Lett.*, 2019, **10**, 3488–3494.
- 383 Y. Li, X. Deng, J. Tian, Z. Liang and H. Cui, *Appl. Mater. Today*, 2018, **13**, 217–227.
- 384 A. Xiong, G. Ma, K. Maeda, T. Takata, T. Hisatomi, T. Setoyama, J. Kubota and K. Domen, *Catal. Sci. Technol.*, 2014, **4**, 325–328.
- 385 Q. Wang, Y. Li, T. Hisatomi, M. Nakabayashi, N. Shibata, J. Kubota and K. Domen, *J. Catal.*, 2015, **328**, 308–315.
- 386 D. Luo, J. Huang, Y. Jian, A. Singh, A. Kumar, J. Liu, Y. Pan and Q. Ouyang, *J. Mater. Chem. B*, 2023, **11**, 6802–6822.
- 387 J. D. Xiao, R. Li and H. L. Jiang, *Small Methods*, 2023, **7**, 2201258.
- 388 Z. Wang, Z. Jin, G. Wang and B. Ma, *Int. J. Hydrogen Energy*, 2018, **43**, 13039–13050.
- 389 M. Zhang, Q. Shang, Y. Wan, Q. Cheng, G. Liao and Z. Pan, *Appl. Catal., B*, 2019, **241**, 149–158.
- 390 X. Yang, Y. Guo, Y. Lou and J. Chen, *Int. J. Hydrogen Energy*, 2021, **46**, 2156–2165.
- 391 L. Liu, S. Du, X. Guo, Y. Xiao, Z. Yin, N. Yang, Y. Bao, X. Zhu, S. Jin, Z. Feng and F. Zhang, *J. Am. Chem. Soc.*, 2022, **144**, 2747–2754.
- 392 S.-Y. Ding and W. Wang, *Chem. Soc. Rev.*, 2013, **42**, 548–568.
- 393 J. Wang and S. Zhuang, *Coord. Chem. Rev.*, 2019, **400**, 213046.
- 394 X. Zhao, P. Pachfule and A. Thomas, *Chem. Soc. Rev.*, 2021, **50**, 6871–6913.
- 395 Q. Yang, M. Luo, K. Liu, H. Cao and H. Yan, *Appl. Catal., B*, 2020, **276**, 119174.
- 396 Y. Yang, X. Chu, H.-Y. Zhang, R. Zhang, Y.-H. Liu, F.-M. Zhang, M. Lu, Z.-D. Yang and Y.-Q. Lan, *Nat. Commun.*, 2023, **14**, 593.
- 397 Y. Wan, L. Wang, H. Xu, X. Wu and J. Yang, *J. Am. Chem. Soc.*, 2020, **142**, 4508–4516.
- 398 P. Xue, W. Chen, M. Tang, Z. Wang and Z. Wang, *Mol. Catal.*, 2023, **535**, 112807.
- 399 W. Chen, L. Wang, D. Mo, F. He, Z. Wen, X. Wu, H. Xu and L. Chen, *Angew. Chem.*, 2020, **132**, 17050–17057.
- 400 S. Yang, H. Lv, H. Zhong, D. Yuan, X. Wang and R. Wang, *Angew. Chem.*, 2022, **134**, e202115655.
- 401 J. Chen, X. Tao, C. Li, Y. Ma, L. Tao, D. Zheng, J. Zhu, H. Li, R. Li and Q. Yang, *Appl. Catal., B*, 2020, **262**, 118271.
- 402 Y. Zhao, S. Zhang, R. Shi, G. I. Waterhouse, J. Tang and T. Zhang, *Mater. Today*, 2020, **34**, 78–91.
- 403 Y. Zhao, G. I. Waterhouse, G. Chen, X. Xiong, L.-Z. Wu, C.-H. Tung and T. Zhang, *Chem. Soc. Rev.*, 2019, **48**, 1972–2010.
- 404 L. Mohapatra and K. Parida, *J. Mater. Chem. A*, 2016, **4**, 10744–10766.
- 405 X. Lu, H. Xue, H. Gong, M. Bai, D. Tang, R. Ma and T. Sasaki, *Nano-Micro Lett.*, 2020, **12**, 1–32.
- 406 G. Fan, F. Li, D. G. Evans and X. Duan, *Chem. Soc. Rev.*, 2014, **43**, 7040–7066.
- 407 Z. Yang, F. Wang, C. Zhang, G. Zeng, X. Tan, Z. Yu, Y. Zhong, H. Wang and F. Cui, *RSC Adv.*, 2016, **6**, 79415–79436.



- 408 M. Wu, J. Wu, J. Zhang, H. Chen, J. Zhou, G. Qian, Z. Xu, Z. Du and Q. Rao, *Catal. Sci. Technol.*, 2018, **8**, 1207–1228.
- 409 S. Megala, M. Sathish, S. Harish, M. Navaneethan, S. Sohila, B. Liang and R. Ramesh, *Appl. Surf. Sci.*, 2020, **509**, 144656.
- 410 C. Wang, B. Ma, S. Xu, D. Li, S. He, Y. Zhao, J. Han, M. Wei, D. G. Evans and X. Duan, *Nano Energy*, 2017, **32**, 463–469.
- 411 A. Rahman and M. M. Khan, *New J. Chem.*, 2021, **45**, 19622–19635.
- 412 P. Feng, X. Bu and N. Zheng, *Acc. Chem. Res.*, 2005, **38**, 293–303.
- 413 K. Mitchell and J. A. Ibers, *Chem. Rev.*, 2002, **102**, 1929–1952.
- 414 M.-R. Gao, Y.-F. Xu, J. Jiang and S.-H. Yu, *Chem. Soc. Rev.*, 2013, **42**, 2986–3017.
- 415 Y.-L. Zhu, J.-H. Yuan, Y.-Q. Song, S. Wang, K.-H. Xue, M. Xu, X.-M. Cheng and X.-S. Miao, *J. Mater. Sci.*, 2019, **54**, 11485–11496.
- 416 F. Liu, F. Xue, Y. Si, G. Chen, X. Guan, K. Lu and M. Liu, *ACS Appl. Nano Mater.*, 2021, **4**, 759–768.
- 417 T. K. Townsend, N. D. Browning and F. E. Osterloh, *ACS Nano*, 2012, **6**, 7420–7426.
- 418 J. Xu, C. Pan, T. Takata and K. Domen, *Chem. Commun.*, 2015, **51**, 7191–7194.
- 419 D. W. Hwang, H. G. Kim, J. Kim, K. Y. Cha, Y. G. Kim and J. S. Lee, *J. Catal.*, 2000, **193**, 40–48.
- 420 C. Wang, B. Ma, S. Xu, D. Li, S. He, Y. Zhao, J. Han, M. Wei, D. G. Evans and X. Duan, *Nano Energy*, 2017, **32**, 463–469.
- 421 X. Cai, L. Mao, M. Fujitsuka, T. Majima, S. Kasani, N. Wu and J. Zhang, *Nano Res.*, 2022, **15**, 438–445.
- 422 W. Deng, X. Hao, Y. Shao, S. Guo and Z. Jin, *Sep. Purif. Technol.*, 2023, **323**, 124375.
- 423 P. Dhanasekaran and N. Gupta, *Int. J. Hydrogen Energy*, 2012, **37**, 4897–4907.
- 424 A. Kudo and H. Kato, *Chem. Phys. Lett.*, 2000, **331**, 373–377.
- 425 Y. Xu, Z. Zhou, P. Yu and Y. Wang, *Chem. Eng. J.*, 2023, **470**, 144275.
- 426 T. Oshima, D. Lu, O. Ishitani and K. Maeda, *Angew. Chem.*, 2015, **127**, 2736–2740.
- 427 W. Shi, F. Guo, C. Zhu, H. Wang, H. Li, H. Huang, Y. Liu and Z. Kang, *J. Mater. Chem. A*, 2017, **5**, 19800–19807.
- 428 X. Ning, W. Zhen, Y. Wu and G. Lu, *Appl. Catal., B*, 2018, **226**, 373–383.
- 429 D. Wang, Z. Zou and J. Ye, *Chem. Mater.*, 2005, **17**, 3255–3261.
- 430 W. Liu, L. Cao, W. Cheng, Y. Cao, X. Liu, W. Zhang, X. Mou, L. Jin, X. Zheng and W. Che, *Angew. Chem.*, 2017, **129**, 9440–9445.
- 431 L. Gao, Y. Li, J. Ren, S. Wang, R. Wang, G. Fu and Y. Hu, *Appl. Catal., B*, 2017, **202**, 127–133.
- 432 H. Pang, W. Zhou, H. Hu, L. Liu, J. Ye and D. Wang, *Appl. Catal., A*, 2023, **654**, 119084.
- 433 K. Gao, H. Guo, Y. Hu, H. He, M. Li, X. Gao and F. Fu, *J. Energy Chem.*, 2023, **87**, 568–582.
- 434 K. Maeda, T. Takata, M. Hara, N. Saito, Y. Inoue, H. Kobayashi and K. Domen, *J. Am. Chem. Soc.*, 2005, **127**, 8286–8287.
- 435 J. Liu, H. Zhang, D. Tang, X. Zhang, L. Yan, Y. Han, H. Huang, Y. Liu and Z. Kang, *ChemCatChem*, 2014, **6**, 2634–2641.
- 436 R. Kobayashi, K. Kurihara, T. Takashima, B. Ohtani and H. Irie, *J. Mater. Chem. A*, 2016, **4**, 3061–3067.
- 437 F. Guo, W. Shi, C. Zhu, H. Li and Z. Kang, *Appl. Catal., B*, 2018, **226**, 412–420.
- 438 M. K. Nazeeruddin, F. De Angelis, S. Fantacci, A. Selloni, G. Viscardi, P. Liska, S. Ito, B. Takeru and M. Grätzel, *J. Am. Chem. Soc.*, 2005, **127**, 16835–16847.
- 439 S. Chai, S.-H. Wen, J.-D. Huang and K.-L. Han, *J. Comput. Chem.*, 2011, **32**, 3218–3225.
- 440 F. De Angelis, S. Fantacci and A. Selloni, *Nanotechnology*, 2008, **19**, 424002.
- 441 J. Chen, H. Zhang, I. V. Tomov, M. Wolfsberg, X. Ding and P. M. Rentzepis, *J. Phys. Chem. A*, 2007, **111**, 9326–9335.
- 442 J. L. Mancuso, A. M. Mroz, K. N. Le and C. H. Hendon, *Chem. Rev.*, 2020, **120**, 8641–8715.
- 443 V. Etacheri, C. Di Valentin, J. Schneider, D. Bahnemann and S. C. Pillai, *J. Photochem. Photobiol., C*, 2015, **25**, 1–29.
- 444 S. Kizito, T. Lv, S. Wu, Z. Ajmal, H. Luo and R. Dong, *Sci. Total Environ.*, 2017, **592**, 197–205.
- 445 D. Waroquiers, A. Lherbier, A. Miglio, M. Stankovski, S. Poncé, M. J. T. Oliveira, M. Giantomassi, G.-M. Rignanese and X. Gonze, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2013, **87**, 075121.
- 446 S. Kizito, H. Luo, S. Wu, Z. Ajmal, T. Lv and R. Dong, *J. Environ. Manage.*, 2017, **201**, 260–267.
- 447 L. Hedin and S. Lundqvist, in *Solid State Phys*, ed. F. Seitz, D. Turnbull and H. Ehrenreich, Academic Press, 1970, vol. 23, pp. 1–181.
- 448 W. G. Aulbur, L. Jönsson and J. W. Wilkins, in *Solid State Phys*, ed. H. Ehrenreich and F. Spaepen, Academic Press, 2000, vol. 54, pp. 1–218.
- 449 S. Ahmed, H. U. Rehman, Z. Ali, A. Qadeer, A. Haseeb and Z. Ajmal, *Surf. Interfaces*, 2021, **23**, 100953.
- 450 A. D. Becke and E. R. Johnson, *J. Chem. Phys.*, 2006, **124**, 221101.
- 451 F. Tran and P. Blaha, *Phys. Rev. Lett.*, 2009, **102**, 226401.
- 452 Y. Zhang, Q. Pan, G. Chai, M. Liang, G. Dong, Q. Zhang and J. Qiu, *Sci. Rep.*, 2013, **3**, 1943.
- 453 V. Etacheri, C. Di Valentin, J. Schneider, D. Bahnemann and S. C. Pillai, *J. Photochem. Photobiol., C*, 2015, **25**, 1–29.
- 454 H. Ye, J. Lee, J. S. Jang and A. J. Bard, *J. Phys. Chem. C*, 2010, **114**, 13322–13328.
- 455 K. T. Butler, Y. Kumagai, F. Oba and A. Walsh, *J. Mater. Chem. C*, 2016, **4**, 1149–1158.
- 456 Y. Wu, P. Lazic, G. Hautier, K. Persson and G. Ceder, *Energy Environ. Sci.*, 2013, **6**, 157–168.
- 457 X. Liu, A. L. Sobolewski, R. Borrelli and W. Domcke, *Phys. Chem. Chem. Phys.*, 2013, **15**, 5957–5966.

