

## High-turnover visible-light photoreduction of CO<sub>2</sub> by a Re(i) complex stabilized on dye-sensitized TiO<sub>2</sub><sup>†</sup>

Cite this: *Chem. Commun.*, 2014, 50, 4462

Received 24th December 2013,  
Accepted 7th March 2014

DOI: 10.1039/c3cc49744e

[www.rsc.org/chemcomm](http://www.rsc.org/chemcomm)

Eun-Gyeong Ha,<sup>a</sup> Jeong-Ah Chang,<sup>a</sup> Sung-Min Byun,<sup>a</sup> Chyongjin Pac,<sup>\*b</sup>  
Dong-Myung Jang,<sup>a</sup> Jeunghee Park<sup>\*a</sup> and Sang Ook Kang<sup>\*a</sup>

**Hybrid systems prepared by fixing a Re(i) complex and a dye on three types of TiO<sub>2</sub> nanoparticles in two different ways commonly revealed persistent photocatalysis of the CO<sub>2</sub> reduction to CO with no levelling-off tendency under visible-light irradiation in DMF, giving a turnover number of  $\geq 435$ .**

The visible-light photoreduction of CO<sub>2</sub> has been receiving considerable interest not only from environmental and long-term energy-security viewpoints,<sup>1</sup> but also as a crucial scientific issue in “artificial photosynthesis”.<sup>2,3</sup> An essential requirement for CO<sub>2</sub> reduction in artificial photosynthesis is to couple the visible-light-driven flow of electrons with multiple-electron chemical processes that can lead to the formation C–H and C–C bonds and can cleave C–O bonds. Such processes require suitable catalysts, among which transition-metal complexes have been regarded as a potential candidate in artificial photosynthesis<sup>4</sup> as well as in electrochemistry,<sup>5</sup> due to the easy tuning of redox potentials, the trapping of CO<sub>2</sub> via its coordination to the metal centre, and the valence jump of the metal oxidation state in response to the multiple-electron reduction processes.

Among a variety of metal complexes investigated,<sup>2–5</sup> the (bpy)Re<sup>I</sup>(CO)<sub>3</sub>Cl (bpy = 2,2'-bipyridine) complex reported by Lehn and his coworkers in 1983 is of particular interest because of the highly selective photoreduction of CO<sub>2</sub> to CO in a relatively high quantum yield.<sup>6</sup> Since then, related Re(i) complexes have been extensively applied to photochemical<sup>7</sup> and electrochemical<sup>8</sup> reductions of CO<sub>2</sub>. However, a serious drawback of the Re(i) complexes in the homogeneous-solution photocatalysis is their short durability, as revealed by leveling-off tendencies in the CO formation at a relatively early stage<sup>7,9</sup> due

to degradation of the Re(i) complexes.<sup>10</sup> However, the degradation might not arise from the inherent properties of the Re(i) complexes, since high turnover numbers were reported for particular systems using sensitizer-bridged Re(i) supramolecules<sup>11</sup> or a sensitizer of cyclic Re(i) trimer and a Re(i) catalyst.<sup>12</sup> In homogeneous solutions, various intermediates<sup>9,13</sup> involving long-lived reactive species are unintentionally distributed to undergo intermolecular interactions associated with the degradation of the starting complex. It can therefore be expected that the fixing of a Re(i) complex on dye-sensitized semiconductors might allow each Re(i) molecule to work as an intrinsic catalyst under visible-light sensitization by the dye. An additional benefit of utilizing such semiconductor-based hybrid systems would derive from the potential capability of semiconductor materials in multiple-electron deposition and transfer to a catalyst site.<sup>3,14</sup> This communication reports that hybrid systems prepared by immobilizing the Re(i) complex **ReC** on dye-loaded TiO<sub>2</sub> nanoparticles reveal persistent behaviour in the photoreduction of CO<sub>2</sub> to CO under visible-light irradiation in the presence of an electron donor (SD) (Fig. 1), and some interesting findings from this work are presented.

The organic dye (Dye), Re(i) catalysts (**ReC** and **ReE**) and electron donor (SD) shown in Fig. 1 were prepared according to known methods (see ESI<sup>†</sup>). The TiO<sub>2</sub> materials used include

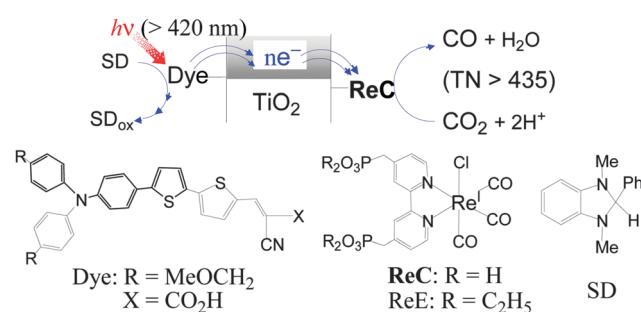


Fig. 1 Conceptual representation for the reaction system (top) and the compounds used in this work (bottom).

<sup>a</sup> Department of Advanced Materials Chemistry, Korea University, 2511 Sejong-ro, Sejong-city 339-700, Korea. E-mail: parkjh@korea.ac.kr, sangok@korea.ac.kr

<sup>b</sup> Yulchon Research Center, Korea University, Sejong-ro 2511, Sejong-city 339-700, Korea. E-mail: jjpac@korea.ac.kr

<sup>†</sup> Electronic supplementary information (ESI) available: Experimental details, IR spectra and DRS of **ReC**/H-TiO<sub>2</sub>/Dye, plots of TN(CO) versus time for the hybrid systems and SEM images of the TiO<sub>2</sub> sources. See DOI: 10.1039/c3cc49744e

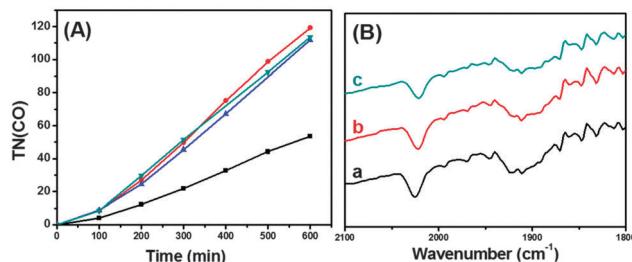


Fig. 2 (A) Plots of CO formation versus time in the absence (—■—) and presence of 1.5 M 2,2,2-trifluoroethanol (—●—), 3% (v/v) H<sub>2</sub>O (—▲—), and 10% (v/v) H<sub>2</sub>O (—▼—) for 10 mg ReC (0.1  $\mu$ mol)/H-TiO<sub>2</sub>/Dye (1.5  $\mu$ mol) in 3 mL DMF containing 0.1 M SD; irradiation at  $>420$  nm. (B) IR spectra of ReC/H-TiO<sub>2</sub>/Dye in KBr discs (sample: KBr  $\approx$  1:100) before (a) and after irradiation for 100 min (b) and for 20 h (c).

synthetic nanosheets with exposed [001] facets (S-TiO<sub>2</sub>) and two commercially available nanosize powders, Hombikat UV-100 (H-TiO<sub>2</sub>) and Degussa P-25 (D-TiO<sub>2</sub>), onto which ReC and Dye were covalently fixed through the phosphonic or carboxylic acid anchoring group. The hybrid materials are denoted as ReC/TiO<sub>2</sub>/Dye when prepared by the initial loading of ReC followed by fixing of the Dye and as Dye/TiO<sub>2</sub>/ReC, which was obtained by the reverse sequence of loading. The successful anchoring of ReC and Dye on the TiO<sub>2</sub> surface was confirmed by IR and diffuse-reflectance absorption spectroscopy (Fig. S1†). Suspensions of the hybrid materials in CO<sub>2</sub>-saturated *N,N*-dimethylformamide (DMF) containing SD (0.1 M) were irradiated at  $>420$  nm using a Xenon lamp combined with a glass light filter.

As shown in Fig. 2(A) and Fig. S2† for the plots of TN(CO) (=molar ratio of CO formed/ReC used) versus irradiation time, CO was steadily formed with no levelling-off tendency; H<sub>2</sub> evolution was only  $<5\%$  that of CO. Table 1 lists TN(CO) after 10 h of irradiation. In the case of ReC/H-TiO<sub>2</sub>/Dye, the steady CO formation continued for 20 h with TN(CO) of 160 (Fig. S3†), and no substantial loss in the IR absorption bands of the CO ligands of ReC was observed (Fig. 2(B)). Formic acid and oxalic acid as the other possible reduction products were not detected upon HPLC analysis of the liquid phase.

For comparison, the photoreduction of CO<sub>2</sub> in homogeneous DMF solution using a combination of ReE/triethanolamine (TEOA), ReE/SD or Ru(bpy)<sub>3</sub><sup>2+</sup>/ReE/SD was undertaken; the CO formation leveled off within 5 h with TN(CO) of  $<50$  (Fig. S4†). These results clearly demonstrate that ReC has been remarkably stabilized by its fixation onto the Dye-loaded TiO<sub>2</sub> nanoparticles. Presumably, two-electron transfers to the ReC site would be effectively mediated through TiO<sub>2</sub> to complete the catalytic cycle without significant degradation of ReC. On the other hand, in

Table 1 Turnover number of CO formation (TN(CO))<sup>a</sup>

ReC/TiO <sub>2</sub> /Dye			Dye/TiO <sub>2</sub> /ReC		
S-TiO <sub>2</sub>	H-TiO <sub>2</sub>	D-TiO <sub>2</sub>	S-TiO <sub>2</sub>	H-TiO <sub>2</sub>	D-TiO <sub>2</sub>
70 (85)	53 (113)	51 (84)	111 (118)	55 (116)	93 (n.d.) <sup>b</sup>

<sup>a</sup> Average values after 10 h irradiation. In parenthesis are the values for the reactions in the presence of 10% (v/v) H<sub>2</sub>O. <sup>b</sup> Not determined.

homogeneous solutions, the second electron transfer to a key intermediate following the first one-electron reduction event should proceed under direct interactions with the second electron source(s), typically the one-electron reduced species of the Re(i) catalyst<sup>9</sup> and oxidized donor radicals, so that unfavourable competitive reactions might occur even to a minor extent.

While the electron flow in the CO<sub>2</sub> reduction should follow the scheme shown in Fig. 1, the relative energy levels of the components need to be referred to. The flat-band potential of a fused-particle TiO<sub>2</sub> electrode in DMF was reported to lie at  $-2.04$  V versus SCE ( $-2.42$  V versus Fc<sup>+0</sup>),<sup>15</sup> which is 0.42 eV more negative than the oxidation potential of excited-singlet Dye (<sup>1</sup>Dye\*).<sup>16</sup> If this were the case, the electron injection from <sup>1</sup>Dye\* into the conduction band of TiO<sub>2</sub> would hardly compete with the decay of <sup>1</sup>Dye\* ( $\tau \approx 1$  ns).<sup>16</sup> Furthermore, the electron transfer to ReC through TiO<sub>2</sub> should be exergonic enough to compete with fast charge recombination.<sup>17</sup> Therefore, the conduction-band minimum of our TiO<sub>2</sub> materials in DMF might be located between the oxidation potential of <sup>1</sup>Dye\* ( $\approx -2$  V versus Fc<sup>+0</sup>)<sup>17</sup> and the reduction potential of ReC ( $-1.67$  V). The oxidation potential of SD ( $-0.185$  V) is much more negative than that of Dye (0.50 V) so that the Dye radical cation left after electron injection from <sup>1</sup>Dye\* into TiO<sub>2</sub> might be efficiently reduced by SD.

Some interesting features from the present observations should be noted. (1) The photocatalytic efficiencies significantly depend on the TiO<sub>2</sub> sources (Table 1), probably related, at least in part, to the different morphologies and crystal phases of the nanoparticles (Fig. S5 and S6†). S-TiO<sub>2</sub> has an anatase nanosheet morphology (20 nm length  $\times$  5 nm thickness) with  $\approx 90\%$  [001] facets, whereas H-TiO<sub>2</sub> (pure anatase) and D-TiO<sub>2</sub> (75% anatase and 25% rutile) are spherical nanoparticles of 5 nm and 18 nm diameter, respectively. The agglomerates of the different nanoparticles should have different distributions of surface states/trap sites and grain boundaries associated with the catalytic properties. (2) In the cases of S- and D-TiO<sub>2</sub>, the initial loading of Dye resulted in considerably higher catalytic activity than the initial loading of ReC, whereas such a loading-sequence effect was not clear in the case of H-TiO<sub>2</sub> (Table 1 and Fig. S1†). A possible assumption is that the surfaces of larger-size S- and D-TiO<sub>2</sub> would have local distributions with different activities in the electron injection from <sup>1</sup>Dye\* and/or electron transfer to ReC, while the surface of smaller-size pure anatase H-TiO<sub>2</sub> would be relatively homogeneous. (3) The reaction efficiencies were considerably enhanced on addition of 1.5 M 2,2,2-trifluoroethanol or 3–10% (v/v) H<sub>2</sub>O, particularly in the cases of the hybrids based on H-TiO<sub>2</sub> and D-TiO<sub>2</sub> (Table 1). This observation is reminiscent of the Brønsted acid effect on electrochemical CO<sub>2</sub> reduction.<sup>18</sup> Such an effect was minor, but appreciable, for the S-TiO<sub>2</sub> hybrids. (4) The CO<sub>2</sub> reduction was almost completely retarded by 1.2 M TEOA, unlike homogeneous-solution CO<sub>2</sub> reduction which is more or less assisted by TEOA coexisting with a real electron donor.<sup>11,12</sup>

In order to confirm the catalytic persistency of the hybrids, we carried out repetitive irradiation experiments. As shown in

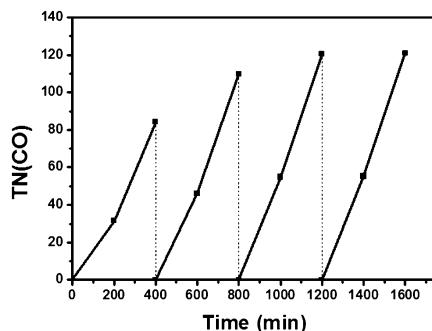


Fig. 3 Formation of CO in a 4-cycle repetition of irradiation at  $>420$  nm for 400 min after  $\text{CO}_2$  bubbling for 30 min in the dark; 10 mg Dye/S-TiO<sub>2</sub>/ReC with 0.1  $\mu\text{mol}$  ReC and 1.5  $\mu\text{mol}$  Dye in the presence of 0.1 M SD and 10% (v/v)  $\text{H}_2\text{O}$ .

Fig. 3 for Dye/H-TiO<sub>2</sub>/ReC, no leveling-off tendency was observed in each cycle and the efficiency of CO formation increased with the increase of the cycle from a TN(CO) of 84 in the 1st run to a TN(CO) of 121 in the 4th run. The total TN(CO) reached 435. The other hybrids also revealed similar behaviour as well (Fig. S8<sup>†</sup>). This unique phenomenon appears to be in line with the appearance of induction periods in Fig. 2, Fig. S2–S4, S7, and S8.<sup>†</sup> While investigations are now being performed on the mechanistic origin, we tentatively assume that the electron transfer to ReC would progressively prevail over electron trapping as various electron-trapping sites distributed in TiO<sub>2</sub><sup>17,19</sup> have been sequentially filled with trapped electrons.

The present investigation has demonstrated that the ReC catalyst immobilized on Dye-sensitized TiO<sub>2</sub> particles works as a persistent catalyst for the reduction of CO<sub>2</sub> to CO with high TN(CO) under visible-light irradiation. It is implied that the convenient methodology reported here might provide a possible way for manifesting the “inherent” catalytic ability of particular transition-metal complexes that would be masked in homogeneous-solution catalysis. A further attempt is currently being made to find stable hybrid systems that can efficiently work in water, directed at coupling the CO<sub>2</sub> reduction hybrid with a water-oxidation system.

This research was supported by a Korea University Grant.

## Notes and references

- 1 S. Styring, *Faraday Discuss.*, 2012, **155**, 357; A. M. Appel, J. E. Bercaw, A. B. Bocarsly, H. Dobbek, D. L. Dubois, M. Dupuis, J. G. Ferry, E. Fujita, R. Hille, P. J. Kenis, C. A. Kerfeld, R. H. Morris, C. H. Peden, A. R. Portis, S. R. Ragasdale, T. B. Rauchfues, J. N. H. Reek, L. C. Seefeldt, R. K. Thauer and G. L. Waldrop, *Chem. Rev.*, 2013, **113**, 6621.
- 2 T. Yui, Y. Tamaki, K. Sekigawa and O. Ishitani, *Top. Curr. Chem.*, 2011, **303**, 151.
- 3 L. Alibabai, H. Luo, R. L. House, P. G. Hoeltz, R. Lopez and T. J. Meyer, *J. Mater. Chem. A*, 2013, **1**, 4133.
- 4 A. J. Morris, G. J. Meyer and E. Fujita, *Acc. Chem. Res.*, 2009, **42**, 1983; J. Schneider, H. Jia, J. T. Muckerman and E. Fujita, *Chem. Soc. Rev.*, 2012, **41**, 2036.
- 5 K. Tanaka and D. Ooyama, *Coord. Chem. Rev.*, 2002, **226**, 211; J.-M. Savéant, *Chem. Rev.*, 2008, **108**, 2348; E. E. Benson, C. P. Kubiak, A. J. Sathrum and J. M. Smieja, *Chem. Soc. Rev.*, 2009, **38**, 89; C. Constantini, M. Robert and J.-M. Savéant, *Chem. Soc. Rev.*, 2013, **42**, 2423.
- 6 J. Hawecker, J.-M. Lehn and R. Ziessel, *J. Chem. Soc., Chem. Commun.*, 1983, 536; J. Hawecker, J.-M. Lehn and R. Ziessel, *Helv. Chim. Acta*, 1986, **69**, 1990.
- 7 H. Takeda, K. Koike, T. Morimoto, H. Inumaru and O. Ishitani, *Adv. Inorg. Chem.*, 2011, **63**, 137; H. M. Sung-Suh, D. S. Kim, C. W. Kim, C. W. Lee and S.-E. Park, *Appl. Organomet. Chem.*, 2000, **14**, 826; P. Kurz, B. Probst, B. Spingler and R. Alberto, *Eur. J. Inorg. Chem.*, 2006, 2966; C. Wang, Z. Xie, K. E. deKraft and W. Lin, *J. Am. Chem. Soc.*, 2011, **133**, 13445; C. Liu, K. D. Dubois, M. E. Lois, A. S. Vorushilov and G. Li, *ACS Catal.*, 2013, **3**, 655; G. A. Andrade, A. J. Pistner, G. P. A. Yap, G. A. Lutterman and J. Rosenthal, *ACS Catal.*, 2013, **3**, 1685.
- 8 J. Hawecker, J.-M. Lehn and R. Ziessel, *J. Chem. Soc., Chem. Commun.*, 1984, 328; J. R. O’toole, L. D. Margelum, T. D. Westmoreland, W. J. Vining, R. W. Murray and T. J. Meyer, *J. Chem. Soc., Chem. Commun.*, 1985, 1416; B. K. Kumar, J. M. Smieja, A. F. Sasayama and C. P. Kubiak, *Chem. Commun.*, 2012, **48**, 272.
- 9 H. Takeda, K. Koike, H. Inoue and O. Ishitani, *J. Am. Chem. Soc.*, 2008, **130**, 2023.
- 10 C. Katal, M. A. Weber, G. Ferraudi and G. Geiger, *Organometallics*, 1985, **4**, 2161; C. Katal, A. J. Corbin and G. Ferraudi, *Organometallics*, 1987, **6**, 553; O. Ishitani, I. Namura, S. Yanagida and C. Pac, *J. Chem. Soc., Chem. Commun.*, 1987, 1153.
- 11 B. Gholamkhass, H. Mametsuka, K. Koike, T. Tanabe, M. Furue and O. Ishitani, *Inorg. Chem.*, 2005, **44**, 2326; Z.-Y. Bian, K. Sumi, M. Furue, S. Sato, K. Koike and O. Ishitani, *Dalton Trans.*, 2009, 983; Y. Tamaki, K. Watanabe, K. Koike, H. Inoue and O. Ishitani, *Faraday Discuss.*, 2012, **155**, 115; Y. Tamaki, K. Koike, T. Morimoto and O. Ishitani, *J. Catal.*, 2013, **304**, 22.
- 12 T. Morimoto, C. Nishiura, M. Tanaka, J. Rohacova, Y. Nakagawa, Y. Funada, K. Koike, Y. Yamamoto, S. Shishido, T. Kojima, T. Saeki, T. Ozeki and O. Ishitani, *J. Am. Chem. Soc.*, 2013, **135**, 13266.
- 13 B. P. Sullivan and T. J. Meyer, *J. Chem. Soc., Chem. Commun.*, 1984, 1244; B. P. Sullivan, C. M. Bolinger, D. Conrad, W. J. Vining and T. J. Meyer, *J. Chem. Soc., Chem. Commun.*, 1985, 1414; D. H. Gibson, X. Yin, H. He and M. S. Mashuta, *Organometallics*, 2003, **22**, 337; Y. Hayashi, S. Kita, B. S. Brunschwig and E. Fujita, *J. Am. Chem. Soc.*, 2003, **125**, 11976; K. D. Dubois, A. Petushkov, E. G. Cardona, S. C. Larsen and G. Li, *J. Phys. Chem. Lett.*, 2012, **3**, 486.
- 14 T. W. Woolerton, S. Sheard, F. Reisner, E. Pierce, S. W. Ragasdale and F. A. Armstrong, *J. Am. Chem. Soc.*, 2010, **132**, 2123; Y. S. Chaudhary, T. W. Woolerton, C. S. Allen, T. H. Warner, E. Pierce, S. W. Ragasdale and F. A. Armstrong, *Chem. Commun.*, 2012, **48**, 58.
- 15 G. Redmond and D. F. Fitzmaurice, *J. Phys. Chem.*, 1993, **97**, 1426.
- 16 S.-H. Lee, Y. Park, K. R. Wee, H. J. Son, D. W. Cho, C. Pac, W. Choi and S. O. Kang, *Org. Lett.*, 2010, **12**, 460.
- 17 W.-S. Han, K.-R. Wee, H.-Y. Kim, C. Pac, Y. Nabetani, D. Yamamoto, T. Shimada, H. Inoue, H. Choi, K. Cho and S. O. Kang, *Chem. – Eur. J.*, 2012, **18**, 16368.
- 18 J. M. Smieja and C. P. Kubiak, *Inorg. Chem.*, 2010, **49**, 9283.
- 19 A. L. Linsebigler, G. Lu and J. T. Yates Jr., *Chem. Rev.*, 1995, **95**, 735; J. R. Durrant, S. A. Haque and J. R. Plomares, *Coord. Chem. Rev.*, 2004, **248**, 1247.