



## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)

# Ion transport in polymerized ionic liquids: a comparison of polycation and polyanion systems

Javad Jeddi,<sup>a</sup> Jukka Niskanen,<sup>b</sup> Benoît H. Lessard  <sup>\*cd</sup>  
and Joshua Sangoro  <sup>\*a</sup>

Received 29th March 2024, Accepted 15th May 2024

DOI: 10.1039/d4fd00070f

The correlation among chemical structure, mesoscale structure, and ion transport in 1,2,3-triazole-based polymerized ionic liquids (polyILs) featuring comparable polycation and polyanion backbones is investigated by wide-angle X-ray scattering (WAXS), differential scanning calorimetry, and broadband dielectric spectroscopy (BDS). Above the glass transition temperature,  $T_g$ , higher ionic conductivity is observed in polycation polyILs compared to their polyanion counterparts, and ion conduction is enhanced by increasing the counterion volume in both polycation or polyanion polyILs. Below  $T_g$ , polyanions show lower activation energy associated with ion conduction. However, the validity of the Barton–Nakajima–Namikawa relation indicates that hopping conduction is the dominant charge transport mechanism in all the polyILs studied. While a significant transition from a Vogel–Fulcher–Tammann to Arrhenius type of thermal activation is observed below  $T_g$ , the decoupling index, often used to quantify the extent to which segmental dynamics and ion conduction are correlated, remains unaltered for the polyILs studied, suggesting that this index may not be a general parameter to characterize charge transport in polymerized ionic liquids. Furthermore, detailed analyses of the WAXS results indicate that both the mobile ion type and the structure of the pendant groups control mesoscale organization. These findings are discussed within the framework of recent models, which account for the subtle interplay between electrostatic and elastic forces in determining ion transport in polyILs. The findings demonstrate the intricate balance between the chemical structure and interactions in polyILs that determine ion conduction in this class of polymer electrolytes.

<sup>a</sup>Department of Chemical and Biomolecular Engineering Ohio State University, Columbus, Ohio 43210, USA.  
E-mail: sangoro.1@osu.edu

<sup>b</sup>Department of Chemical and Metallurgical Engineering, Aalto University, Kemistintie 1, 02150 Espoo, Finland

<sup>c</sup>Department of Chemical and Biological Engineering, University of Ottawa, 161 Louis Pasteur, Ottawa, Ontario K1N 6N5, Canada. E-mail: benoit.lessard@uottawa.ca

<sup>d</sup>School of Electrical Engineering and Computer Science, University of Ottawa, 800 King Edward Ave, Ottawa, ON, K1N 6N5, Canada




Polymerized ionic liquids (polyILs) are a new class of polymer electrolytes combining promising ion conduction, electrochemical stability, and thermal stability of ionic liquids (ILs) with the mechanical properties of polymers for different applications such as solar cells, lithium-ion rechargeable batteries, fuel cells, actuators, electrochromic devices, and electronic transistors.<sup>1–10</sup> The ionic conductivity, one of the most important properties of polyILs, is sensitive to different factors such as the chemical structure of the cation and anion, length, and type of spacer between the polymer backbone and chemically bonded ion, molecular architecture, degree of polymerization, and ion density.<sup>11–22</sup> In contrast to molecular ILs, the ionic conductivity of polyILs drops by several orders of magnitude upon polymerization, limiting their use in many applications.<sup>3</sup> Previous studies of polyILs have mainly focused on attempts to understand ion transport mechanisms in systems where the cations are tethered to the polymeric chain.<sup>3,18,22,23</sup> One of the key findings is that ionic conduction in polyILs is decoupled from segmental dynamics in contrast to the well-studied polyethylene oxide (PEO) based polymer electrolytes.<sup>23–26</sup> The decoupling is usually highlighted by a transition of the dc ionic conductivity from Vogel–Fulcher–Tammann (VFT) to Arrhenius type of thermal activation below the glass transition temperature,  $T_g$ . For many practical applications such as Li-ion batteries, anionic polyILs are more relevant yet these systems have not been well studied. The extent to which the insights from cationic polyILs apply to their anionic counterparts remains an open question.

One of the peculiar characteristics of organic ionic salts such as ionic liquids and polyILs is the tendency to form distinct structural features due to the mesoscopic organization of ionic, polar, and non-polar moieties.<sup>27–30</sup> Wide-angle X-ray scattering is instrumental in examining the structure of amorphous ionic liquids and polyILs.<sup>30,31</sup> In the polyILs based on alkyl-imidazolium cations, different morphologies of polar and nonpolar domains can form, and the backbone-to-backbone correlation peak is observed to shift to lower  $q$  values with increasing alkyl chain length. These structural features significantly influence ion transport in polycation polyILs.<sup>22,30,32</sup> However, it is unclear if such structural signatures exist and influence charge transport in polyILs with anions tethered on the polymer backbones.

In this study, four model 1,2,3-triazole-based polyILs with either polycation or polyanion backbones comprising comparable chemical structures, are investigated to understand the impact of mobile ion types and chemical structure of the backbone on the correlation between mesoscopic organization and ionic conductivity. A combination of broadband dielectric spectroscopy (BDS) and X-ray scattering techniques are employed to elucidate the effects of the chemistry of anionic and cationic backbone structures and ion dynamics. It is found that a subtle interplay between the chemical structure and interactions in polyILs determines the ion conduction in both classes of polyILs.

The model 1,2,3-triazole-based polymerized ionic liquids (polyILs) studied in this work include poly(1-(4-vinyl benzyl)-1*H*-1,2,3-triazole-4-yl)methanesulfonate) with 1-butyl-3-methyl-imidazolium ( $C_4MIm^+$ ) and  $Na^+$  as the cations (PVB- $SO_3^-C_4MIm$  and PVB- $SO_3^-Na$ ), poly(4-butyl-3-methyl-1-(4-vinyl benzyl)-1*H*-1,2,3-triazol-3-ium chloride) (PVB-MeCl), and poly(4-butyl-3-methyl-1-(4-vinylbenzyl)-1*H*-1,2,3-triazol-3-ium TFSI) (PVB-MeTFSI). These systems were synthesized using a copper-catalyzed azidealkyne cycloaddition (CuAAC) ‘click’ reaction as reported



previously.<sup>33</sup> The thermal properties were characterized using differential scanning calorimetry (DSC). DSC measurements of polyIL samples were carried out using a TA Instruments DSC2500 unit calibrated with indium (temperature and enthalpy) and sapphire (heat capacity). The samples were dried in a vacuum oven at 350 K for 24 hours before sealing in the Tzero aluminum hermetic pans. Standard heat-cool-heat cycles at 10 K min<sup>-1</sup> were applied to determine the glass transition temperatures,  $T_g$ s. The  $T_g$  was considered as the midpoint of the step in the second heating cycle.

A Novocontrol High-Resolution Alpha Dielectric Analyzer equipped with a Quatro Cryosystem for temperature control was employed for the BDS measurements in the frequency range 0.1–10<sup>7</sup> Hz. The samples were prepared by thermomechanically pressing between two Teflon sheets to obtain a film of about 10 mm in diameter. The films were sandwiched between two polished brass electrodes in a parallel plate configuration. The sample thickness was kept constant at 100  $\mu$ m using silica spacers, then annealed at 350 K for 24 h in a vacuum oven to remove moisture before starting the BDS measurements. In the dielectric analyzer, the samples were further annealed at 375 K under dry nitrogen gas while the dielectric response was continuously monitored until a plateau in the real part of the complex dielectric function *versus* time at various frequency points, was reached. The Quatro Cryosystem was employed to control the temperature of the samples within  $\pm 0.1$  K accuracy of the set point.

The X-ray scattering experiments were conducted in the transmission mode using a Xenocs Xeuss 3.0 X-ray scattering instrument equipped with a Cu K $\alpha$  50 kV Xenocs Genix ULD SL X-ray source ( $\lambda = 1.5418$  Å) at room temperature. Pressed sample films (100  $\mu$ m) were dried in a vacuum oven at 350 K for 24 h before starting the measurement to minimize the moisture effect on the results. The two-dimensional scattering patterns were registered in a PILATUS3 R 300K detector from Dectris, Ltd. The scattered intensity was obtained as a function of the scattering vector  $q = (4\pi \sin \theta)/\lambda$ , where  $2\theta$  is the scattering angle through azimuthal averages of the 2D data in the given angular range.

The chemical structures and molecular properties of the polyILs investigated in this work are shown in Fig. 1 and Table 1, respectively. Fig. 2 shows the differential scanning calorimetry (DSC) thermograph of the polyILs studied in the current work. PVB-MeTFSI shows the lowest  $T_g$  among all systems investigated and this result can be understood at a qualitative level. The glass transition temperature,  $T_g$ , of polyILs is thought to be controlled by cooperative dynamics determined by intermolecular interactions, which can be influenced by free volume or packing effects, coulombic interactions between anions and cations, and molecular weight.<sup>30</sup> For the TFSI<sup>-</sup> anion, the charge delocalization between S–N–S bonds along with steric hindrances from sulfonyl and trifluoromethane groups, results in the reduction of the strength of coulombic interactions with the triazolium cation, leading to a lower  $T_g$ .<sup>22,34,35</sup> However, the high charge density of the Cl<sup>-</sup> anion results in stronger ionic interactions with the triazolium cation, leading to the higher  $T_g$  of PVB-MeCl. Based on similar arguments, the higher  $T_g$  values of the polyanions compared to their polycation counterparts can be rationalized. In both polyanion and polycation systems, larger counterions result in lower  $T_g$ . This observation is consistent with previous studies that explored the counterion charge density in determining  $T_g$  of the polyILs.<sup>4</sup> However, rationalization of the higher  $T_g$  in the polyanions requires a more in-depth study of the



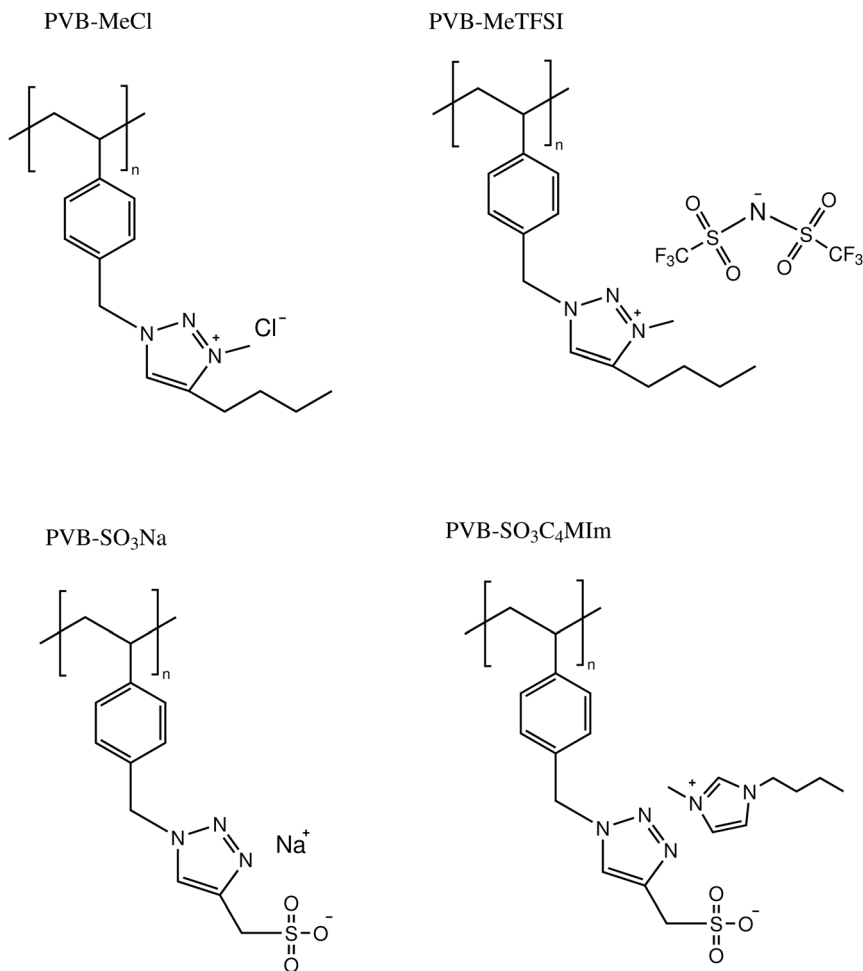



Fig. 1 Chemical structures of the model polymerized ionic liquids studied in this work.

structure, as discussed later based on the wide-angle X-ray scattering (WAXS) results.

Fig. 3 shows the wide-angle X-ray scattering (WAXS) spectra presented in terms of the intensity *versus* scattering vector (*q*). The characteristic X-ray scattering peaks for the cationic polyILs indicate the rich mesoscale organization associated with polar, non-polar, and ionic moieties.<sup>30,36–39</sup> Through a combination of molecular dynamics simulations and X-ray scattering experiments to analyze the mesoscopic structure in polyILs, three general structural features corresponding to the backbone-to-backbone (low *q*), ion-ion (intermediate *q*), and pendant group (high *q*) correlation distances have been identified.<sup>19,22,30,32,36,40,41</sup>

To quantitatively determine the peak position, asymmetric Lorentzian functions,  $I(q) = \frac{1}{\pi} \frac{\Delta_i}{\Delta_i^2 + (q - q_{0,i})^2} [1 + b_i(q - q_{0,i})]$ , are used to fit the X-ray scattering data.<sup>42,43</sup> This equation represents an asymmetric distribution with the



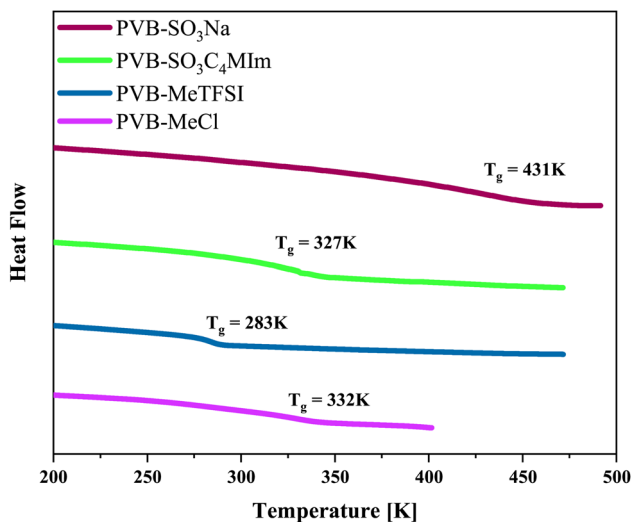


Fig. 2 Differential scanning calorimetry thermograph of the polymerized ionic liquids investigated in the current work.

Table 1 The characteristics of the polymerized ionic liquids investigated in this work


Sample	$M_n$ (g mol <sup>-1</sup> )	$D^a$	DP <sup>b</sup>	$T_g$ (K)
PVB-MeCl	22 800	1.1	78	332 ± 1
PVB-MeTFSI	39 700	1.2	74	283 ± 1
PVB-SO <sub>3</sub> Na	27 100	1.2	90	431 ± 1
PVB-SO <sub>3</sub> C <sub>4</sub> MIm	30 900	1.2	74	327 ± 1

<sup>a</sup>  $D$ : dispersity index. <sup>b</sup> DP: degree of polymerization.

center at  $q_0 = 2\pi/d$ , a full-width at half maximum (FWHM) of  $\Delta$ , and an asymmetric parameter  $b$ . The fit parameters yield characteristic correlation lengths, presented in Table 2.

Despite the similarity of WAXS spectra of polyanion and polycation samples, there are some unique differences. The low- $q$  and intermediate- $q$  peaks of PVB-SO<sub>3</sub>Na appear at lower  $q$  in comparison with polycations. The sharp low- $q$  peak of PVB-SO<sub>3</sub>Na corresponds to the center-to-center spacing between ion aggregates ( $d_{\text{aggregate}}$ ), which is associated with the characteristic length scale of 21.7 Å.<sup>44–47</sup> The intermediate- $q$  peak of correlation distance 13.7 Å may be related to the backbone-to-backbone distance, which is comparable to the polycation counterparts. On the other hand, the broad low- $q$  peak of PVB-SO<sub>3</sub>C<sub>4</sub>MIm that appears in the  $q = 0.31 \text{ \AA}^{-1}$ ,  $d_{\text{aggregate}} = 20.3 \text{ \AA}$ , may be due to the merging of the backbone-to-backbone and ion aggregate peaks. The second intermediate- $q$  peak of PVB-SO<sub>3</sub>-C<sub>4</sub>MIm shows a correlation length scale of 8.24 Å, corresponding to the ion-ion correlation.

The length of the fully stretched pendant groups of polyanion and polycation polyILs were estimated to be 12.25 and 12.5 Å using the open-source Avogadro software. Thus, idealized, fully stretched, non-interdigitated systems should yield



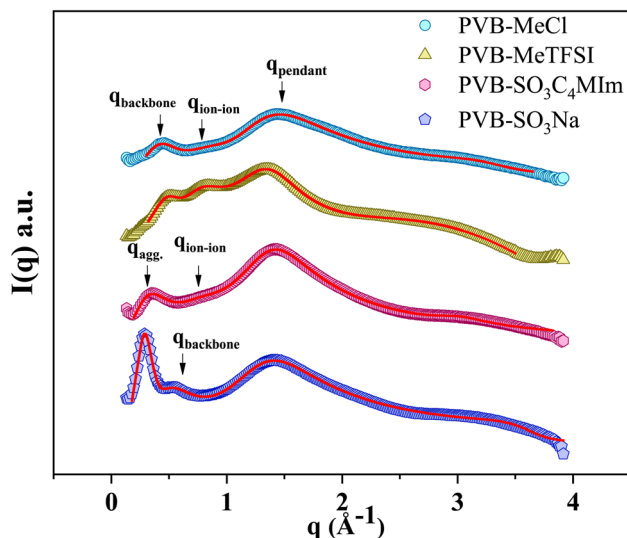


Fig. 3 The wide-angle X-ray scattering intensity versus the wave vector,  $q$ , for the polyILs investigated in the current work at 300 K. The arrows indicate the peak positions associated with the backbone-ion, and pendant-correlation distances. The red solid lines are fits obtained using asymmetric Lorentzian functions.


Table 2 The periodicity,  $d$ , values extracted from the WAXS spectra using the asymmetric Lorentzian model for all the polyILs investigated

	PVB-MeCl	PVB-MeTFSI	PVB-SO <sub>3</sub> C <sub>4</sub> MIm	PVB-SO <sub>3</sub> Na
$d_{\text{backbone}}$ (Å)	$14.85 \pm 0.1$	$12.69 \pm 0.1$	—	$13.68 \pm 0.1$
$d_{\text{ion}}$ (Å)	$7.22 \pm 0.2$	$8.16 \pm 0.2$	$8.24 \pm 0.2$	—
$d_{\text{pendant}}$ (Å)	$4.65 \pm 0.1$	$4.67 \pm 0.1$	$4.51 \pm 0.1$	$4.65 \pm 0.1$

nearly double backbone-to-backbone correlation distances. Although this is a crude estimate, some insights may be gleaned from these values. The comparable pendant group sizes of the polycation and polyanion polyILs agree with  $d_{\text{backbone}}$  values from WAXS, implying interdigitation of the pendant groups. However, the association of  $\text{SO}_3^-$  and the free cations at the end of the pendant group, likely results in large aggregates while the butyl pendant group of the polycations presumably disrupts the ion aggregate formation.<sup>48–50</sup> These ion aggregates can act as physical cross-linking points resulting in the segmental dynamics restriction and higher  $T_g$  in polyanions.

The dielectric spectra of PVB-MeTFSI at different temperatures are shown in Fig. 4. A combination of the empirical Havriliak–Negami (HN) and the random barrier model (RBM) functions were used to describe the dielectric spectra:<sup>51</sup>

$\varepsilon^*(\omega) = \varepsilon_\infty + \frac{\Delta\varepsilon}{[1 + (i\omega\tau)^\alpha]^\gamma} + \frac{\sigma_0}{i\omega\varepsilon_0} \frac{i\omega\tau_e}{\ln(1 + i\omega\tau_e)} + A\omega^n$ , where  $\Delta\varepsilon$  is the dielectric relaxation strength,  $\tau_{\text{HN}}$  is the relaxation time,  $\alpha$  and  $\gamma$  are symmetric and asymmetric stretching parameters of the HN function in the first term. The second term represents the RBM part where  $\sigma_0$  is the dc ionic conductivity,  $\tau_e$  is



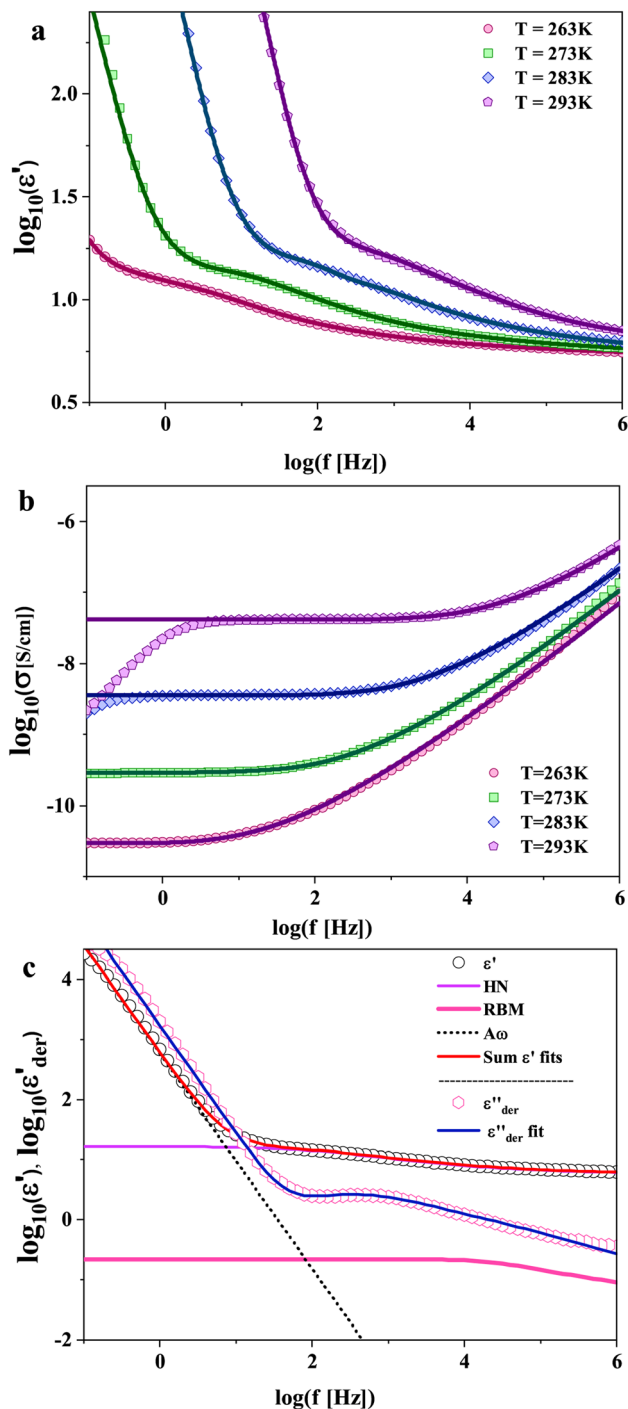


Fig. 4 (a and b) The real parts of the complex dielectric, ( $\epsilon^*(\omega) = \epsilon'(\omega) - i\epsilon''(\omega)$ ), and complex conductivity functions, ( $\sigma^*(\omega) = \sigma'(\omega) + i\sigma''(\omega)$ ), for PVB MeTFSI polymerized ionic liquid at the selected temperatures as indicated. The lines denote fits obtained by combining the Havriliak–Negami function to account for re-orientational ion dynamics,




the characteristic charge transport time,  $\varepsilon_0$  is the vacuum permittivity, and  $\varepsilon_\infty$  is the limiting high-frequency permittivity. The  $A\omega^n$  term is used to account for electrode polarization. The empirical HN model describes the orientational polarization effects associated with ion conduction.<sup>18,19</sup> On the other hand, the RBM model accounts for charge transport. Within the RBM framework, ion hopping occurs by overcoming the spatially randomly distributed energy barriers.<sup>52</sup> Above  $T_g$ , the counterion diffusion in the polyILs is coupled to some degree to the segmental dynamics or  $\alpha$ -relaxation. However, the dielectric relaxations in this spectral range are not detectable due to the dominant contributions of the ionic conductivity to  $\varepsilon''$ . To suppress the dc conductivity contributions, the derivative representation of the imaginary part of the complex dielectric function, defined as  $\varepsilon''_{\text{der}} = -\frac{\pi}{2} \frac{\partial \varepsilon'}{\partial \ln(\omega)}$  based on the Kramers–Kronig relation, is used.

Fig. 5a shows variation in the dc ionic conductivity with the inverse temperature. The high dc conductivity of PVB-MeTFSI and PVBSO<sub>3</sub>C<sub>4</sub>MIm compared to their counterparts correlates with their lower  $T_g$ . The bulky structure of the counterions likely lowers the charge density and coulombic interaction strengths, resulting in faster segmental dynamics of the polymer backbone. To analyze the results at comparable timescales, the dc conductivity is plotted *versus*  $T_g$ -normalized temperature. Above  $T_g$  ( $T_g/T < 1$ ), the conductivity of PVB-MeTFSI is slightly higher while PVBSO<sub>3</sub>C<sub>4</sub>MIm has the lowest conductivity.

This suggests that above  $T_g$ , ion transport is more effective in the PVB-MeTFSI at the same value of  $T_g/T$ . However, we could not study the  $\sigma_{\text{dc}}$  conductivity of PVB-SO<sub>3</sub>Na above  $T_g$  due to the possibility of sample degradation at higher temperatures. The temperature dependence of  $\sigma_0$  above  $T_g$  can be represented by the Vogel–Fulcher–Tammann (VFT) equation  $\sigma_0 = \sigma_\infty \exp\left(\frac{-B}{T - T_0}\right)$ , where  $B$ ,  $\sigma_\infty$ , and  $T_0$  are fitting parameters (Table 3), below  $T_g$ , the Arrhenius equation is employed. Fig. 5b shows the variation of the dc conductivity *versus*  $\omega_c (=1/\tau_c)$  which follows the empirical Barton, Nakajima, and Namikawa (BNN) relation.<sup>51</sup> The BNN relation correlates the dc conductivity to the dielectric relaxation strength through  $\sigma_0 = p\varepsilon_0\Delta\varepsilon\omega_c$ , where  $p$  is a dimensionless empirical number,  $\sigma_0$  is the apparent dc conductivity,  $\Delta\varepsilon$  is the dielectric relaxation strength, and  $\omega_c$  is from the RBM. Fig. 5b suggests that the underlying mechanisms of ion conduction and dielectric relaxation in polyanion and polycation polyILs are similar.<sup>21</sup>

The degree of decoupling,  $m$ , determined at  $T_g$  using  $m = 15 + \log_{10}(\sigma_0)$ , was proposed to quantify the coupling between segmental and ion conduction.<sup>53</sup> The extent of decoupling of the ion conduction from segmental dynamics is dictated by the backbone and pendant group stiffness.<sup>54</sup> The close decoupling indices suggest that the chain stiffness of polycations and polyanions are comparable. In the current study, the effect of the counterions of either the cation or anion on the degree of decoupling is negligible (see Table 3), indicating that  $m$  is likely controlled by the backbone structure. However, a close examination of the

the random barrier model to account for charge transport, and a power-law function to describe interfacial/electrode polarization as described in the text. (c) Representative dielectric spectra of PVB-MeTFSI at  $T = 283$  K together with the different fit functions as indicated.





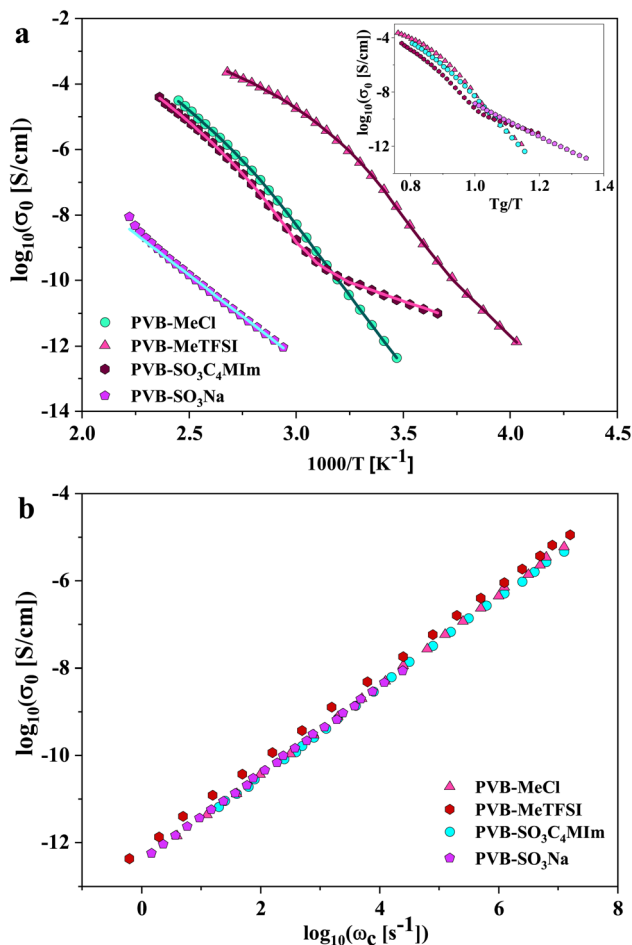


Fig. 5 (a) The dc ionic conductivity,  $\sigma_0$ , versus inverse temperature. The inset plot shows  $\sigma_0$  as a function of  $T_g/T$ , where  $T_g$  denotes the glass transition temperature. This scaling enables a more direct ionic conductivity comparison at identical segmental dynamics timescales. The solid lines show fits obtained using a combination of the Vogel–Fulcher–Tammann and Arrhenius equations. (b) The dc ionic conductivity,  $\sigma_0$ , versus the characteristic charge transport rates,  $\omega_c$ , for the studied poly(L)s showing that the Barton–Nakajima–Namikawa (BNN) relation holds and the hopping conduction is the dominant mechanism of charge transport for both polycations and polyanions.

**Table 3** VFT fitted parameters and activation energy of ionic conductivity and ion–ion correlation lengths of poly(L) samples

Sample	$\sigma_\infty$	$B$	$T_0$	$E_\sigma$ (kJ mol <sup>-1</sup> )	Decoupling index ( $m$ )
PVB-MeCl	64	2927	207	165 ± 1	6.7
PVB-MeTFSI	0.24	1013	227	123 ± 1	6.7
PVB-SO <sub>3</sub> -C <sub>4</sub> MIm	18	2702	217	43 ± 1	5.9
PVB-SO <sub>3</sub> Na	—	—	—	95 ± 1	6.1




remarkable differences below  $T_g$  implies that  $m$  may not be an appropriate parameter for characterizing ion transport in polyILs.

The  $E_\sigma$  values can be calculated from the temperature dependence of ionic conductivity below the  $T_g$  using the Arrhenius equation  $\sigma_0 = \sigma_\infty \exp\left(\frac{-E_a}{RT}\right)$ , where  $\sigma_\infty$  is a pre-exponential factor and  $R$  is the universal gas constant. More accurate estimates are obtained by the fitting data in a broad range of temperatures by combining the VFT and Arrhenius equations. Despite the comparable decoupling indices, polyanion polyILs show lower ion conduction activation energy,  $E_\sigma$ , than their polycation counterparts. Moreover, smaller counterions result in higher  $E_\sigma$  in polycation and polyanion polyILs. Deeper insights into the ion conduction properties of the polyILs can be gleaned by attempting to find correlations between their ion transport properties below  $T_g$  and their chemical structure.

In the polyanion systems, the strong coulombic interactions within the ion aggregates result in slower segmental dynamics, as reflected by the  $T_g$  values. Below  $T_g$ , polyanion systems show lower ion activation energy than their polycation counterparts. This result is presumably associated with the percolation of the ion aggregates. We conjecture that the larger characteristic lengths associated with the ion aggregates of the polyanions lead to frustrations in the packing of the polymeric chains and form percolated ion paths resulting in facilitated ion mobility below  $T_g$ . On the other hand, the interdigitation of butyl pendant groups leads to better-packed structures and steric hindrances that limit the available sites for ion hopping as reflected by the higher  $E_\sigma$ .

The counterion size is another factor that controls the  $E_\sigma$ . The overall effect of the counterion size and charge density on the  $E_\sigma$  can be interpreted using the Anderson–Stuart Model. Within the framework of this model, the activation energy is given by:<sup>55,56</sup>  $E_\sigma = \frac{\beta q_1 q_2}{4\pi\epsilon_0\epsilon(R_1 + R_2)} + 4\pi G\lambda(R_1 - R_D)^2$ , where the first term describes the coulombic interactions between mobile ions with charge,  $q_1$  and radius  $R_1$ , and counterions with charge  $q_2$  and radius  $R_2$ .  $\epsilon_0$  and  $\epsilon$  are vacuum permittivity and medium static dielectric permittivity, and  $\beta$  is the Madelung constant. The second term defines the elastic contribution of the ion jump process. The  $G$  term is the shear modulus,  $R_D$  is the radius of free volume for ion hopping, and  $\lambda$  is the ion jump length. In the polycation systems, it is observed that the  $E_\sigma$  of PVB-MeCl is higher than PVB-MeTFSI. The small size of  $\text{Cl}^-$  results in stronger coulombic interactions with the triazolium ring. So, according to this model, the coulombic term dominates the  $E_\sigma$ . It was previously shown that the elastic modulus of polyILs increases with the ionic volume of the counteranion.<sup>57</sup> However, the lower  $E_\sigma$  of PVB-MeTFSI correspond to the weaker coulombic interactions of the large TFSI<sup>-</sup> and backbone despite higher shear modulus.

The higher  $E_\sigma$  of PVB-SO<sub>3</sub>Na than PVB-SO<sub>3</sub>C<sub>4</sub>MIm can also be understood using the Anderson–Stuart Model. The strong coulombic interaction of the Na<sup>+</sup> and polyanion backbone enhances  $E_\sigma$ . On the other hand, C<sub>4</sub>MIm<sup>+</sup> can increase the shear modulus and decrease the coulombic interaction. The low  $E_\sigma$  indicates the effect of the weaker coulombic interaction dominates the higher shear modulus role in controlling ion conduction activation energy. This microscopic understanding of ion dynamics in polymerized ionic liquids will be valuable in



designing solid polymer electrolytes. These results suggest that a subtle counterbalance between electrostatic and elastic forces determines the overall ionic conduction. A rational design of polyILs for practical applications should involve carefully selecting the target ionic groups that optimize the total contribution of these forces in a wide range of temperatures.

In summary, differential scanning calorimetry (DSC), broadband dielectric spectroscopy (BDS), and wide-angle X-ray scattering (WAXS) were employed to understand the correlation between chemical structure, nanoscale organization, and ion transport properties of 1,2,3-triazole based polymerized ionic liquids. Above  $T_g$ , polycation polyILs showed higher ion conduction compared to anionic backbone counterparts due to the coupling of the ion conduction and segmental dynamics. Below  $T_g$ , polyanions show lower  $E_\sigma$  of ion conduction than their polycation counterpart. The strong coulombic interactions between the backbone and the counterions result in higher  $E_\sigma$  while increasing the volume of the counterion leads to higher shear modulus and reduction of the  $E_\sigma$ , qualitatively consistent with the Anderson–Stuart model. The findings of this work provide insights into the rational design of solid electrolytes.

## Conflicts of interest


There are no conflicts to declare.

## Acknowledgements


This work was supported by the National Science Foundation for financial support through the Division of Materials Research award DMR-2327018. We thank the Natural Sciences and Engineering Research Council of Canada (NSERC) Discovery grant RGPIN 2020-04079 (B. H. L.), the Canada Research Chairs Program 950-230724 (B. H. L.).

## References


- 1 H. Ohno, Design of Ion Conductive Polymers Based on Ionic Liquids, *Macromol. Symp.*, 2007, **249–250**, 551–556.
- 2 H. Ohno, M. Yoshizawa and W. Ogihara, Development of new class of ion conductive polymers based on ionic liquids, *Electrochim. Acta*, 2004, **50**, 255–261.
- 3 J. R. Sangoro, C. Iacob, A. Agapov, Y. Wang, S. Berdzinski, H. Rexhausen, V. Strehmel, C. Friedrich, A. Sokolov and F. Kremer, Decoupling of ionic conductivity from structural dynamics in polymerized ionic liquids, *Soft Matter*, 2014, **10**, 3536–3540.
- 4 D. Mecerreyes, Polymeric ionic liquids: Broadening the properties and applications of polyelectrolytes, *Prog. Polym. Sci.*, 2011, **36**, 1629–1648.
- 5 B. Yang, G. Yang, Y.-M. Zhang and S. X.-A. Zhang, Recent advances in poly (ionic liquid) s for electrochromic devices, *J. Mater. Chem. C*, 2021, **9**, 4730–4741.
- 6 M. N. Tousignant, M. Ourabi, J. Niskanen, B. Mirka, W. J. Bodnaryk, A. Adronov and B. H. Lessard, Poly (ionic liquid) dielectric for high




- performing P-and N-type single walled carbon nanotube transistors, *Flexible Printed Electron.*, 2022, **7**, 034004.
- 7 N. J. Dallaire, B. Mirka, J. G. Manion, W. J. Bodnaryk, D. Fong, A. Adronov, K. Hinzner and B. H. Lessard, Conjugated wrapping polymer influences on photoexcitation of single-walled carbon nanotube-based thin film transistors, *J. Mater. Chem. C*, 2023, **11**, 9161–9171.
  - 8 A. J. Peltekoff, S. Brixi, J. Niskanen and B. H. Lessard, Ionic liquid containing block copolymer dielectrics: designing for high-frequency capacitance, low-voltage operation, and fast switching speeds, *JACS Au*, 2021, **1**, 1044–1056.
  - 9 A. J. Peltekoff, V. E. Hiller, G. P. Lopinski, O. A. Melville and B. H. Lessard, Unipolar polymerized ionic liquid copolymers as high-capacitance electrolyte gates for n-type transistors, *ACS Appl. Polym. Mater.*, 2019, **1**, 3210–3221.
  - 10 J. Niskanen, M. N. Tousignant, A. J. Peltekoff and B. H. Lessard, Poly (ethylene glycol)-Based Poly (ionic liquid) Block Copolymers through 1, 2, 3-Triazole Click Reactions, *ACS Appl. Polym. Mater.*, 2022, **4**, 1559–1564.
  - 11 Z. Zhang, N. Marioni, H. S. Sachar and V. Ganesan, Polymer Architecture-Induced Trade-off between Conductivities and Transference Numbers in Salt-Doped Polymeric Ionic Liquids, *ACS Macro Lett.*, 2023, **12**, 1351–1357.
  - 12 M. Cotessat, D. Flachard, D. Nosov, E. I. Lozinskaya, D. O. Ponkratov, D. F. Schmidt, E. Drockenmuller and A. S. Shaplov, Effects of repeat unit charge density on the physical and electrochemical properties of novel heterocationic poly (ionic liquid) s, *New J. Chem.*, 2021, **45**, 53–65.
  - 13 J. R. Keith, N. J. Rebello, B. J. Cowen and V. Ganesan, Influence of counterion structure on conductivity of polymerized ionic liquids, *ACS Macro Lett.*, 2019, **8**, 387–392.
  - 14 C. M. Evans, C. R. Bridges, G. E. Sanoja, J. Bartels and R. A. Segalman, Role of tethered ion placement on polymerized ionic liquid structure and conductivity: pendant versus backbone charge placement, *ACS Macro Lett.*, 2016, **5**, 925–930.
  - 15 Y. Fu, V. Bocharova, M. Ma, A. P. Sokolov, B. G. Sumpster and R. Kumar, Effects of counterion size and backbone rigidity on the dynamics of ionic polymer melts and glasses, *Phys. Chem. Chem. Phys.*, 2017, **19**, 27442–27451.
  - 16 F. Fan, W. Wang, A. P. Holt, H. Feng, D. Uhrig, X. Lu, T. Hong, Y. Wang, N.-G. Kang and J. Mays, others Effect of molecular weight on the ion transport mechanism in polymerized ionic liquids, *Macromolecules*, 2016, **49**, 4557–4570.
  - 17 F. Fan, Y. Wang, T. Hong, M. F. Heres, T. Saito and A. P. Sokolov, Ion conduction in polymerized ionic liquids with different pendant groups, *Macromolecules*, 2015, **48**, 4461–4470.
  - 18 M. A. Harris, M. F. Heres, J. Coote, A. Wenda, V. Strehmel, G. E. Stein and J. Sangoro, Ion transport and interfacial dynamics in disordered block copolymers of ammonium-based polymerized ionic liquids, *Macromolecules*, 2018, **51**, 3477–3486.
  - 19 M. Heres, T. Cosby, E. U. Mapesa, H. Liu, S. Berdzinski, V. Strehmel, M. Dadmun, S. J. Paddison and J. Sangoro, Ion transport in glassy polymerized ionic liquids: Unraveling the impact of the molecular structure, *Macromolecules*, 2019, **52**, 88–95.
  - 20 E. U. Mapesa, M. Chen, M. F. Heres, M. A. Harris, T. Kinsey, Y. Wang, T. E. Long, B. S. Lokitz and J. R. Sangoro, Charge transport in imidazolium-



- based homo-and triblock poly (ionic liquid) s, *Macromolecules*, 2019, **52**, 620–628.
- 21 U. H. Choi, Y. Ye, D. Salas de la Cruz, W. Liu, K. I. Winey, Y. A. Elabd, J. Runt and R. H. Colby, Dielectric and viscoelastic responses of imidazolium-based ionomers with different counterions and side chain lengths, *Macromolecules*, 2014, **47**, 777–790.
  - 22 C. Iacob, A. Matsumoto, M. Brennan, H. Liu, S. J. Paddison, O. Urakawa, T. Inoue, J. Sangoro and J. Runt, Polymerized ionic liquids: Correlation of ionic conductivity with nanoscale morphology and counterion volume, *ACS Macro Lett.*, 2017, **6**, 941–946.
  - 23 V. Bocharova and A. P. Sokolov, Perspectives for polymer electrolytes: a view from fundamentals of ionic conductivity, *Macromolecules*, 2020, **53**, 4141–4157.
  - 24 C. Imrie, M. Ingram and G. McHattie, Ion transport in glassy polymer electrolytes, *J. Phys. Chem. B*, 1999, **103**, 4132–4138.
  - 25 J. Bartels, G. E. Sanoja, C. M. Evans, R. A. Segalman and M. E. Helgeson, Decoupling mechanical and conductive dynamics of polymeric ionic liquids via a trivalent anion additive, *Macromolecules*, 2017, **50**, 8979–8987.
  - 26 S. Cheng, Z. Wojnarowska, J. Sangoro and M. Paluch, Ion dynamics in pendant and backbone polymerized ionic liquids: A view from high-pressure dielectric experiments and free-volume model, *Phys. Rev. E*, 2022, **105**, 054502.
  - 27 O. Russina, A. Triolo, L. Gontrani and R. Caminiti, Mesoscopic structural heterogeneities in room-temperature ionic liquids, *J. Phys. Chem. Lett.*, 2012, **3**, 27–33.
  - 28 O. Russina, F. L. Celso, M. Di Michiel, S. Passerini, G. Appetecchi, F. Castiglione, A. Mele, R. Caminiti and A. Triolo, Evidences of fluorinated nano-domains in room temperature ionic liquids with perfluoroalkylsulfonylimide anions, *Faraday Discuss.*, 2013, **499**, 167.
  - 29 L. Gontrani, P. Ballirano, F. Leonelli and R. Caminiti, X-ray diffraction studies of ionic liquids: from spectra to structure and back, *The Structure of Ionic Liquids*, 2014, pp. 1–37.
  - 30 D. S.-D. la Cruz, M. D. Green, Y. Ye, Y. A. Elabd, T. E. Long and K. I. Winey, Correlating backbone-to-backbone distance to ionic conductivity in amorphous polymerized ionic liquids, *J. Polym. Sci., Part B: Polym. Phys.*, 2012, **50**, 338–346.
  - 31 A. Triolo, O. Russina, H.-J. Bleif and E. Di Cola, Nanoscale segregation in room temperature ionic liquids, *J. Phys. Chem. B*, 2007, **111**, 4641–4644.
  - 32 S. Li, J. L. Bañuelos, J. Guo, L. Anovitz, G. Rother, R. W. Shaw, P. C. Hillesheim, S. Dai, G. A. Baker and P. T. Cummings, Alkyl chain length and temperature effects on structural properties of pyrrolidinium-based ionic liquids: a combined atomistic simulation and small-angle X-ray scattering study, *J. Phys. Chem. Lett.*, 2012, **3**, 125–130.
  - 33 J. Niskanen, M. N. Tousignant, A. J. Peltekoff and B. H. Lessard, 1, 2, 3-Triazole based poly (ionic liquids) as solid dielectric materials, *Polymer*, 2021, **212**, 123144.
  - 34 J. Leys, R. N. Rajesh, P. C. Menon, C. Glorieux, S. Longuemart, P. Nockemann, M. Pellens and K. Binnemans, Influence of the anion on the electrical conductivity and glass formation of 1-butyl-3-methylimidazolium ionic liquids, *J. Chem. Phys.*, 2010, **133**, 034503.



- 35 A. Pipertzis, G. Papamokos, M. Mühlinghaus, M. Mezger, U. Scherf and G. Floudas, What determines the glass temperature and dc-conductivity in imidazolium-polymerized ionic liquids with a polythiophene backbone?, *Macromolecules*, 2020, **53**, 3535–3550.
- 36 H. Liu and S. J. Paddison, Direct comparison of atomistic molecular dynamics simulations and X-ray scattering of polymerized ionic liquids, *ACS Macro Lett.*, 2016, **5**, 537–543.
- 37 C. F. Buitrago, J. E. Jenkins, K. L. Oppen, B. S. Aitken, K. B. Wagener, T. M. Alam and K. I. Winey, Room temperature morphologies of precise acid-and ion-containing polyethylenes, *Macromolecules*, 2013, **46**, 9003–9012.
- 38 M. E. Seitz, C. D. Chan, K. L. Oppen, T. W. Baughman, K. B. Wagener and K. I. Winey, Nanoscale morphology in precisely sequenced poly (ethylene-co-acrylic acid) zinc ionomers, *J. Am. Chem. Soc.*, 2010, **132**, 8165–8174.
- 39 H. V. Annapureddy, H. K. Kashyap, P. M. De Biase and C. J. Margulis, What is the origin of the prepeak in the X-ray scattering of imidazolium-based room-temperature ionic liquids?, *J. Phys. Chem. B*, 2010, **114**, 16838–16846.
- 40 J. C. Araque, J. J. Hettige and C. J. Margulis, Modern room temperature ionic liquids, a simple guide to understanding their structure and how it may relate to dynamics, *J. Phys. Chem. B*, 2015, **119**, 12727–12740.
- 41 K. M. Beers and N. P. Balsara, Design of Cluster-free Polymer Electrolyte Membranes and Implications on Proton Conductivity, *ACS Macro Lett.*, 2012, **1**, 1155–1160.
- 42 H. Weiss, J. Mars, H. Li, G. Kircher, O. Ivanova, A. Feoktystov, O. Soltwedel, M. Bier and M. Mezger, Mesoscopic correlation functions in heterogeneous ionic liquids, *J. Phys. Chem. B*, 2017, **121**, 620–629.
- 43 D. Pontoni, M. DiMichiel and M. Deutsch, Nanoscale Structure in Short-Chain Ionic Liquids, *ChemPhysChem*, 2020, **21**, 1887–1897.
- 44 B. A. Paren, N. Nguyen, V. Ballance, D. T. Hallinan, J. G. Kennemur and K. I. Winey, Superionic Li-ion transport in a single-ion conducting polymer blend electrolyte, *Macromolecules*, 2022, **55**, 4692–4702.
- 45 E. G. Sorte, B. A. Paren, C. G. Rodriguez, C. Fujimoto, C. Poirier, L. J. Abbott, N. A. Lynd, K. I. Winey, A. L. Frischknecht and T. M. Alam, Impact of hydration and sulfonation on the morphology and ionic conductivity of sulfonated poly (phenylene) proton exchange membranes, *Macromolecules*, 2019, **52**, 857–876.
- 46 Z. Zhang, C. Liu, X. Cao, J.-H. H. Wang, Q. Chen and R. H. Colby, Morphological evolution of ionomer/plasticizer mixtures during a transition from ionomer to polyelectrolyte, *Macromolecules*, 2017, **50**, 963–971.
- 47 B. A. Paren, B. A. Thurston, W. J. Neary, A. Kendrick, J. G. Kennemur, M. J. Stevens, A. L. Frischknecht and K. I. Winey, Percolated ionic aggregate morphologies and decoupled ion transport in precise sulfonated polymers synthesized by ring-opening metathesis polymerization, *Macromolecules*, 2020, **53**, 8960–8973.
- 48 A. Agrawal, D. Perahia and G. S. Grest, Cluster morphology-polymer dynamics correlations in sulfonated polystyrene melts: computational study, *Phys. Rev. Lett.*, 2016, **116**, 158001.
- 49 S. Kang and M. J. Park, 100th Anniversary of Macromolecular Science Viewpoint: Block Copolymers with Tethered Acid Groups: Challenges and Opportunities, *ACS Macro Lett.*, 2020, **9**, 1527–1541.



- 50 J. Park, A. Staiger, S. Mecking and K. I. Winey, Structure–Property Relationships in Single-Ion Conducting Multiblock Copolymers: A Phase Diagram and Ionic Conductivities, *Macromolecules*, 2021, **54**, 4269–4279.
- 51 F. Kremer and A. Schönhals, *Broadband Dielectric Spectroscopy*, Springer Science & Business Media, 2002.
- 52 J. C. Dyre, P. Maass, B. Roling and D. L. Sidebottom, Fundamental questions relating to ion conduction in disordered solids, *Rep. Prog. Phys.*, 2009, **72**, 046501.
- 53 C. Austen Angell, Concepts and conflicts in polymer electrolytes: The search for ion mobility, *Electrochim. Acta*, 2019, **313**, 205–210.
- 54 Z. Wojnarowska, H. Feng, Y. Fu, S. Cheng, B. Carroll, R. Kumar, V. N. Novikov, A. M. Kisliuk, T. Saito, N.-G. Kang and Others, Effect of chain rigidity on the decoupling of ion motion from segmental relaxation in polymerized ionic liquids: Ambient and elevated pressure studies, *Macromolecules*, 2017, **50**, 6710–6721.
- 55 O. Anderson and D. Stuart, Calculation of activation energy of ionic conductivity in silica glasses by classical methods, *J. Am. Ceram. Soc.*, 1954, **37**, 573–580.
- 56 K. Kumbhakar, T. D. Pham, K.-K. Lee, K. Kwak and M. Cho, Dielectric Relaxation Spectroscopy for the Characterization of Ion Transport in Solid Polymer Electrolytes in Li-ion Cells, *Electrochim. Acta*, 2023, **462**, 142759.
- 57 A. Matsumoto, C. Iacob, T. Noda, O. Urakawa, J. Runt and T. Inoue, Introducing large counteranions enhances the elastic modulus of imidazolium-based polymerized ionic liquids, *Macromolecules*, 2018, **51**, 4129–4142.

