

# ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

## Discrete and Encapsulated Molecular Grids: Homometallic Mn<sub>15</sub> and Heterometallic Mn<sub>24</sub>Ni<sub>2</sub> Aggregates

Maria Charalambous,<sup>a</sup> Sotiris M. Zartilas,<sup>a</sup> Eleni E. Moushi,<sup>a</sup> Constantina Papatriantafyllopoulou,<sup>a</sup> Manolis J. Manos,<sup>a</sup> Theocharis C. Stamatatos,<sup>b</sup> Shreya Mukherjee,<sup>b</sup> Vassilios Nastopoulos,<sup>c</sup> George Christou,<sup>b</sup> and Anastasios J. Tasiopoulos\*<sup>a</sup>

Received (in XXX, XXX) Xth XXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXX 20XX

DOI: 10.1039/b000000x

Two molecular grid - like clusters are reported, one is a discrete [3 x 5] grid and the other a [3 x 4] grid within a Mn<sub>12</sub>Ni<sub>2</sub> loop. Both Mn<sub>24</sub>Ni<sub>2</sub> and Mn<sub>15</sub> aggregates display novel and aesthetically pleasing structures with the former one being among the highest nuclearity heterometallic Mn<sub>x</sub>M<sub>y</sub> clusters (M = any transition metal ion).

High nuclearity 3d metal clusters continue to attract significant research interest owing to their intriguing geometrical features (large size, high symmetry, aesthetically pleasing shapes and architectures),<sup>1</sup> fascinating physical properties, including single-molecule magnetism (SMM) behaviour<sup>1, 2</sup> and usefulness as models to probe nanoscopic and mesoscopic phenomena.<sup>3</sup> The intense efforts in this area have resulted in a plethora of polynuclear compounds and SMMs that possess diverse structural topologies, including dimers, triangles, cubanes, tetrahedra, icosahedra, etc.<sup>1</sup> Among these species, the ones with planar metal topologies including wheels, disks and clusters with sheet-like or grid-like conformations have attracted special attention.<sup>4- 6</sup> The significance of such compounds arises from their inherent structural beauty and the fact that they represent excellent model systems for the study of spin frustration and quantum effects.<sup>7</sup> In addition, wheels and grids can be used for the study of one- and two- dimensional magnetism, respectively. Furthermore, molecular grids also constitute model systems for magnets with extended interactions on a square lattice, which have gained significant attention due to their importance in the development of better high-temperature superconductors.<sup>8</sup> However, although there are now many wheels known,<sup>4</sup> clusters with grid-like metal topologies are less common.<sup>6</sup> In fact, the majority of the known molecular grids contain polytopic ligands with suitably disposed coordination pockets that favor the formation of such structural motifs and possess oligomeric structures based on mononuclear repeating units.<sup>6</sup> In these compounds, the metal ions are usually connected through poly-atomic bridges which result in very weak magnetic exchange interactions and low ground state spin values. On the other hand, molecular grids that involve tightly connected metal ions through several monoatomic bridges are very unusual in metal cluster chemistry and would be particularly attractive in the area of molecular magnetism.<sup>6,8</sup>

Herein, we report two new compounds [Mn<sup>IV</sup><sub>12</sub>Mn<sup>III</sup><sub>12</sub>Ni<sup>II</sup><sub>2</sub>O<sub>30</sub>(EtCO<sub>2</sub>)<sub>16</sub>(MeO)<sub>12</sub>(MeOH)<sub>8</sub>(H<sub>2</sub>O)<sub>2</sub>] (1) and

(Me<sub>4</sub>N)<sub>2</sub>[Mn<sup>III</sup><sub>13</sub>Mn<sup>IV</sup><sub>2</sub>O<sub>10</sub>(OH)<sub>2</sub>(mpt)<sub>4</sub>(hmmbd)<sub>2</sub>((CH<sub>3</sub>)<sub>3</sub>CCO<sub>2</sub>)<sub>8</sub>(py)<sub>2</sub>·((CH<sub>3</sub>)<sub>3</sub>CCO<sub>2</sub>)<sub>2</sub>H·2py·3.6MeCN (2·2py·3.6MeCN) (py = pyridine, H<sub>3</sub>mpt = 3-methyl-1,3,5-pentanetriol and H<sub>3</sub>hmmbd = 2-hydroxymethyl-3-methylbutane-1,3-diol) based on uncommon [3 x 4] and [3 x 5] grid - like aggregates respectively that are held together through both monoatomic and polyatomic bridges. They possess several novel structural features with complex 1 displaying an unprecedented “grid-within-a-loop” metal topology and being among the highest nuclearity heterometallic Mn/M (M = any transition metal ion) metal clusters, and the anion of 2 representing a unique example of high oxidation state, mixed-valent Mn<sup>III/IV</sup> molecular grid-like cluster.

The reaction of [Mn<sub>3</sub>O(EtCO<sub>2</sub>)<sub>6</sub>(py)<sub>3</sub>]·(ClO<sub>4</sub>), NiCl<sub>2</sub>·6H<sub>2</sub>O and Bu<sup>n</sup><sub>4</sub>NMnO<sub>4</sub> in a 10 : 30 : 1 molar ratio in MeOH resulted in a red-brown slurry that was filtered to give a dark reddish-brown filtrate. The filtrate was left undisturbed at room temperature for a period of ~ 2 weeks, upon which reddish-brown crystals of 1 were formed in 37% yield; dried solid was analyzed as 1·5H<sub>2</sub>O (for synthetic details see ESI†). The molecular structure<sup>‡</sup> of 1 (Fig. 1) consists of a mixed-metal [Mn<sup>III</sup><sub>12</sub>Ni<sub>2</sub>(μ<sub>3</sub>-O)<sub>12</sub>(EtCO<sub>2</sub>)<sub>16</sub>(μ<sub>3</sub>-MeO)<sub>2</sub>(μ-MeO)<sub>6</sub>(MeOH)<sub>8</sub>(H<sub>2</sub>O)<sub>2</sub>]<sup>8-</sup> loop incorporating a [Mn<sup>IV</sup><sub>12</sub>(μ<sub>3</sub>-O)<sub>14</sub>(μ-O)<sub>4</sub>(μ-MeO)<sub>4</sub>]<sup>8+</sup> [3 x 4] grid-

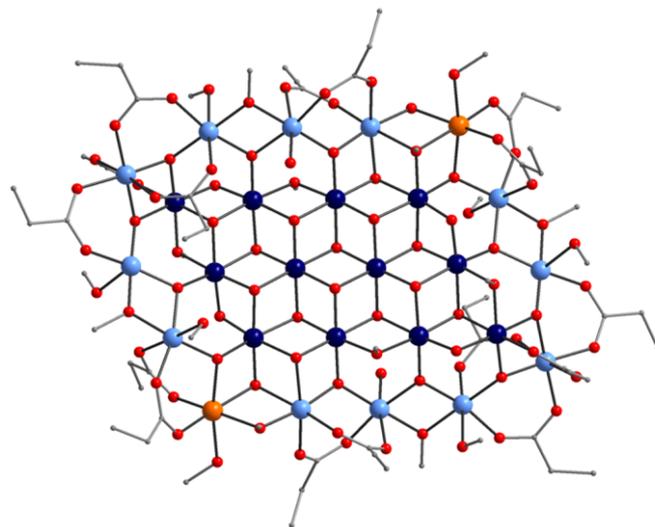
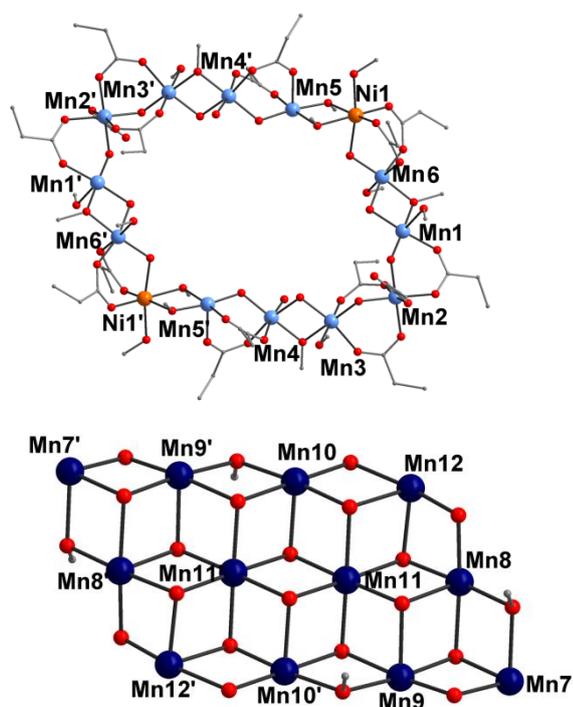


Fig.1 Representation of the molecular structure of 1. Colour code: Mn<sup>III</sup>, light blue; Mn<sup>IV</sup>, dark blue; Ni, orange; O, red; C, grey. H atoms are omitted for clarity.

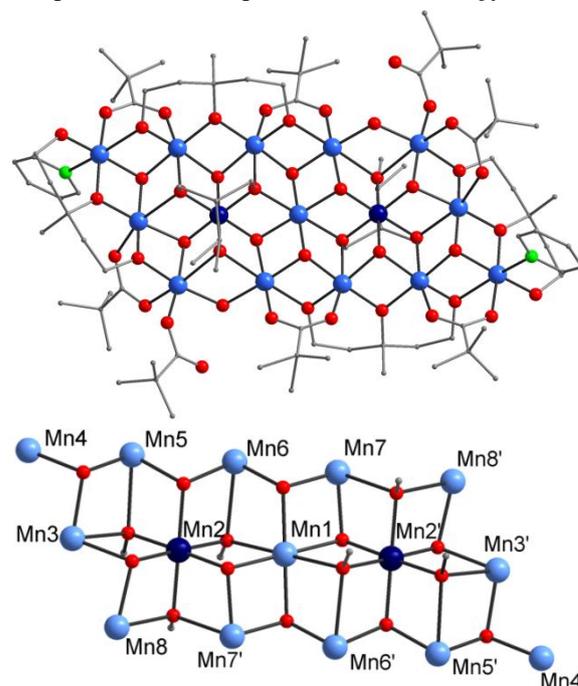


**Fig.2** Representations of the  $\text{Mn}^{\text{III}}_{12}\text{Ni}_2$  loop (top) and  $\text{Mn}^{\text{IV}}_{12}$  [3 x 4] grid-like (bottom) sub-units of **1**. Colour code:  $\text{Mn}^{\text{III}}$ , light blue;  $\text{Mn}^{\text{IV}}$ , dark blue; Ni, orange; O, red; C, grey. H atoms are omitted.

like unit. The  $\text{Mn}^{\text{III}}_{12}\text{Ni}_2$  loop (Fig 2, top) is composed of two symmetry-related  $[\text{Mn}_6\text{NiO}_6(\text{EtCO}_2)_8(\text{MeO})_4(\text{MeOH})_4(\text{H}_2\text{O})]^{4-}$  units, each one containing six  $\text{Mn}^{\text{III}}$  and one  $\text{Ni}^{\text{II}}$  ions held together through six  $\mu_3\text{-O}^{2-}$ , eight  $\eta^1\text{-}\eta^1\text{-}\mu$   $\text{EtCO}_2^-$  ions and three  $\mu$  and one  $\mu_3\text{-MeO}^-$  groups. Their peripheral ligation is completed by four terminal MeOH and one monodentate  $\text{H}_2\text{O}$  molecules. The two  $\text{Mn}_6\text{Ni}$  units are linked through one  $\mu_3\text{-MeO}^-$  and one  $\mu\text{-MeO}^-$  bridges that connect Ni1 and Mn5 atoms at each side forming the  $\text{Mn}_{12}\text{Ni}_2$  loop which adopts an ellipsoid conformation. In the inner cavity of the loop is located a  $\text{Mn}^{\text{IV}}_{12}$  [3 x 4] grid-like unit (Fig 2, bottom) linked to the external ring through fourteen  $\mu_3\text{-O}^{2-}$  ions, two  $\eta^1\text{-}\eta^1\text{-}\mu$   $\text{EtCO}_2^-$  ions and two  $\mu_3\text{-MeO}^-$  bridges. The metal ions in the  $\text{Mn}^{\text{IV}}_{12}$  unit are held together through fourteen  $\mu_3\text{-}$  and four  $\mu\text{-O}^{2-}$  bridges, and four  $\mu\text{-MeO}^-$  groups. The  $\text{Mn}^{\text{IV}}_{12}$  sub-unit consists of twelve edge-sharing  $[\text{Mn}^{\text{IV}}_3\text{O}]^{10+}$  oxo-centered triangular units. Note that the  $\text{Mn}^{\text{IV}}_{12}$  grid-like subunit present in **1** is the highest nuclearity unit consisting of solely  $\text{Mn}^{\text{IV}}$  ions. In addition, the average oxidation state level of the Mn ions of **1** (3.5) is the highest ever observed in large polynuclear clusters (with nuclearity > 20) with the second one being ~3.43 appeared in a  $\text{Mn}^{\text{III}}_{12}\text{Mn}^{\text{IV}}_9$  aggregate.<sup>5d</sup> The oxidation states of the Mn ions and the protonation levels of  $\text{O}^{2-}/\text{MeO}^-/\text{EtCO}_2^-$  groups were determined by bond valence sum (BVS) calculations,<sup>9</sup> charge-balance considerations and inspection of metric parameters. All Mn ions are six-coordinate with near octahedral geometry except from Mn1 atom (and its symmetry equivalent) which is five-coordinate with a distorted square pyramidal coordination geometry; the O17 atom from a terminal MeOH molecule occupies the axial position. The six-coordinate  $\text{Mn}^{\text{III}}$  ions (Mn2 - Mn6) display the expected Jahn – Teller elongation axes which are aligned almost co-parallel. (Fig

S1, ESI<sup>†</sup>).

The reaction of  $[\text{Mn}_3\text{O}((\text{CH}_3)_3\text{CCO}_2)_6(\text{py})_3]$ ,  $\text{H}_3\text{mpt}$  and  $\text{Me}_4\text{NOH}$  in a 1 : 2 : 2 molar ratio in MeCN/py (3:1) resulted in a red-brown slurry which was filtered to give a dark reddish-brown filtrate. The filtrate was left undisturbed at room temperature for a period of ~ 2 weeks, upon which reddish-brown crystals of **2**·2py·3.6MeCN were formed in 25% yield; dried solid was analyzed as **2**·2py·2H<sub>2</sub>O (ESI<sup>†</sup>). Note that although  $\text{H}_3\text{hmmbd}$  ligand was added in the reaction mixture as one of the coexisting branched polyalcohols contained as impurities in commercially available  $\text{H}_3\text{mpt}$ , the synthesis of **2**·2py·3.6MeCN is highly reproducible. The molecular structure<sup>‡</sup> of the anion of **2** (Fig 3) consists of 13  $\text{Mn}^{\text{III}}$  and 2  $\text{Mn}^{\text{IV}}$  ions which are held together through ten  $\mu_3\text{-O}^{2-}$  ions and six  $\mu_3\text{-OR}^-$  groups, the latter coming from the two  $\eta^3\text{-}\eta^3\text{-}\eta^3\text{-}\mu_7$   $\text{hmmbd}^{3-}$  ligands.<sup>9</sup> The Mn ions adopt a planar conformation with the mean deviation from the least-squares plane being ~0.1 Å and the maximum deviation being ~0.3 Å (for the two  $\text{Mn}^{\text{IV}}$  ions, i.e Mn2). The  $\text{Mn}/\text{O}^{2-}$  ( $\text{OR}^-$ ) core consists of 16 edge-sharing  $[\text{Mn}_3(\mu_3\text{-O}(\text{R}))]^{n+}$  triangles whose central  $\text{O}^{2-}$  or  $\text{OR}^-$  groups are located above and below the plane defined by the Mn ions. The grid-like  $[\text{Mn}_{15}(\mu_3\text{-O})_{10}(\mu_3\text{-OR})_6]^{21+}$  core is further bridged in its periphery through two  $\mu\text{-OH}^-$  ions and ten  $\mu\text{-OR}^-$  groups coming from four  $\text{mptl}^{3-}$  ligands. In particular, the five Mn ions in each long edge of the  $\text{Mn}_{15}$  plane are connected through one  $\mu\text{-OH}^-$  and the  $\mu\text{-OR}^-$  arms of an  $\text{mptl}^{3-}$  ligand adopting the  $\eta^2\text{-}\eta^2\text{-}\eta^2\text{-}\mu_4$  coordination mode whereas the three Mn ions in each short edge of the [3 x 5] plane are bridged through the  $\mu\text{-OR}^-$  arms of an  $\text{mptl}^{3-}$  ligand adopting the  $\eta^2\text{-}\eta^2\text{-}\eta^1\text{-}\mu_3$  mode. The peripheral ligation of the metal ions is completed by eight pivalate groups, six of which bridge with the common *syn,syn*- $\eta^1\text{-}\eta^1\text{-}\mu$  coordination mode with the remaining two acting as monodentate ligands, and two terminal py



**Fig.3** Representations of the molecular structure of the anion of **2** (top) and its  $[\text{Mn}_{15}(\mu_3\text{-O})_{10}(\mu_3\text{-OR})_6]^{21+}$  structural core (bottom). Colour code:  $\text{Mn}^{\text{III}}$ , light blue;  $\text{Mn}^{\text{IV}}$ , dark blue; O, red; N, green; C, grey. H atoms are omitted for clarity.

molecules. The charge of the  $[\text{Mn}_{15}]^-$  anion is balanced by two  $\text{Me}_4\text{N}^+$  and one  $(\text{CH}_3)_3\text{CCO}_2)_2\text{H}^+$  counterions in the crystal lattice, the latter consisting of two pivalate anions sharing a proton. All Mn ions are six-coordinate with near octahedral geometry with the  $\text{Mn}^{\text{III}}$  ones displaying the expected Jahn – Teller elongations, although the elongation axes are not all co-parallel. It is noteworthy that the  $\text{Mn}/\text{O}^{2-}$  core of **2** is clearly related to the structures of several salts and minerals including iodides of moderately polarizing cations ( $\text{Cd}^{2+}$ ,  $\text{Mg}^{2+}$ ,  $\text{Ca}^{2+}$ , etc) and hydroxides of dications, i.e. compounds with the general formula  $\text{M}(\text{OH})_2$ .<sup>10</sup>

Direct-current (dc) magnetic susceptibility ( $\chi_M$ ) measurements were performed on powdered crystalline samples of **1**·5H<sub>2</sub>O and **2**·2py·2H<sub>2</sub>O in the 5–300 K range in a 1 kG (0.1 T) magnetic field and are plotted as  $\chi_M T$  vs  $T$  in Fig 4. For both complexes, the profiles of the  $\chi_M T$  versus  $T$  plots are indicative of the presence of competing ferro- and antiferromagnetic exchange interactions between the metal ions. In addition, the  $\chi_M T$  values at low temperatures (**1**·5H<sub>2</sub>O, 10.23 cm<sup>3</sup> K mol<sup>-1</sup>; **2**·2py·2H<sub>2</sub>O, 16.52 cm<sup>3</sup> K mol<sup>-1</sup>) suggest ground-state spin values,  $S_T = 4$  and 5 or 6 for **1**·5H<sub>2</sub>O and **2**·2py·2H<sub>2</sub>O, respectively; the spin-only ( $g = 2$ ) values are 10 and 15 or 21 cm<sup>3</sup> K mol<sup>-1</sup> for  $S_T = 4$  and 5 or 6, respectively.

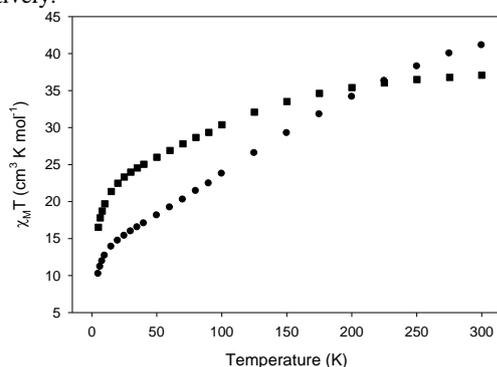


Fig. 4  $\chi_M T$  vs  $T$  plots for **1**·5H<sub>2</sub>O (●) and **2**·2py·2H<sub>2</sub>O (■).

Ac susceptibility studies use no dc field and thus are an excellent complementary tool for determining  $S$  by avoiding potential complications from a large dc field.<sup>2a, 11a</sup> The in-phase susceptibility  $\chi'_M$  data for **1**·5H<sub>2</sub>O and **2**·2py·2H<sub>2</sub>O are shown as  $\chi'_M T$  versus  $T$  plots in Fig S2, ESI†. For **1**·5H<sub>2</sub>O, extrapolation of the  $\chi'_M T$  signal to 0 K from  $T > \sim 8$  K (to avoid the effects of intermolecular interactions at lower temperatures) gives a value of  $\sim 10$  cm<sup>3</sup> K mol<sup>-1</sup> consistent with  $S_T = 4$  and  $g = 2$ . In addition, the out-of-phase ac magnetic susceptibility  $\chi''_M$  versus  $T$  plot for **1**·5H<sub>2</sub>O, at temperatures  $< \sim 2.5$  K (Fig S3, ESI†) displays frequency-dependent signals whose maxima lie below the operating minimum temperature (1.8 K) of our SQUID instrument. This behavior is possibly due to slow relaxation of magnetization, suggesting that **1**·5H<sub>2</sub>O might be a new SMM. For **2**·2py·2H<sub>2</sub>O, extrapolation of the  $\chi'_M T$  to 0 K, from  $T$  above  $\sim 6$  K as in case of **1**·5H<sub>2</sub>O, gave a value of  $\sim 17$ –18 cm<sup>3</sup> K mol<sup>-1</sup> consistent with an  $S_T = 6$  ground state value with  $g < 2$ . No out-of-phase ac signals were observed for **2**·2py·2H<sub>2</sub>O down to 1.8 K.

Magnetization ( $M$ ) data were also collected for **1**·5H<sub>2</sub>O and **2**·2py·2H<sub>2</sub>O in the 0.1–7 T and 1.8–10.0 K ranges, and these are plotted as reduced magnetization ( $M/N\mu_B$ ) vs  $H/T$ . We used only low field data to avoid problems caused by the existence of low –

lying excited states and / or intermolecular interactions.<sup>5b, 11a</sup> For **1**·5H<sub>2</sub>O, it was not possible to obtain a satisfactory fit assuming that only the ground state is populated in this temperature range. This suggests that the complex possesses particularly low-lying excited states, populated even at these relatively low temperatures. For **2**·2py·2H<sub>2</sub>O, an acceptable quality fit was obtained for  $S_T = 6$  with parameters  $g = 1.87(1)$  and  $D = -0.295(1)$  cm<sup>-1</sup> (Fig S4, ESI†). However, the  $g$  and  $D$  values are merely an approximation given the low quality of the fit. Thus, the magnetization data also suggest an  $S_T = 6$  ground state for **2**·2py·2H<sub>2</sub>O.

In conclusion, two new polynuclear compounds based on molecular grid clusters are reported. The first one is a discrete [3 x 5] grid and the other a [3 x 4] grid encapsulated within a  $\text{Mn}^{\text{III}}_{12}\text{Ni}_2$  loop. The discrete  $\text{Mn}_{15}$  cluster is a member of a small class of molecular grids containing several monoatomic bridges and as a consequence tightly connected metal ions. In addition, it represents a unique example of high oxidation state mixed-valent  $\text{Mn}^{\text{III/IV}}$  grid-like cluster. The  $\text{Mn}_{24}\text{Ni}_2$  aggregate possesses an unprecedented “grid-within-a-loop” structural topology, a unique [3 x 4] grid like sub-unit consisting solely of  $\text{Mn}^{\text{IV}}$  ions and a nuclearity that is among the highest yet observed for heterometallic  $\text{Mn}_x\text{M}_y$  clusters being smaller only than these of a  $\text{Mn}_{28}\text{Cu}_{17}$  and a  $\text{Mn}_{36}\text{Ni}_4$  clusters.<sup>11</sup> Its isolation, following on from the construction of a  $\text{Mn}_{36}\text{Ni}_4$  “loop of loops and supertetrahedra” aggregate<sup>11a</sup> proves the potential of mixed Mn/Ni cluster chemistry to afford high nuclearity, aesthetically pleasing structures. Furthermore, the present study establishes  $\text{H}_3\text{mpt}$  as a promising ligand for the isolation of polynuclear Mn complexes with novel crystal structures and magnetic properties. Further studies in both areas are in progress and will be reported in due course.

This work was supported by the Cyprus Research Promotion Foundation Grant “IIENEK/0311/04” which is co-funded by the Republic of Cyprus and the European Regional Development Fund. GC thanks the NSF for support (DMR-1213030). We also thank the European Union Seventh Framework Program (FP7/2007-2013) under Grant agreement numbers: PCIG09-GA-2011-293814 (AJT and CP) and PIRSES-GA-2011-295190 (AJT and MC).

## Notes and references

- <sup>a</sup> Department of Chemistry, University of Cyprus, 1678 Nicosia, Cyprus.  
<sup>90</sup> Fax: +357 22895451; Tel: +357 22892765; E-mail: [atasio@ucy.ac.cy](mailto:atasio@ucy.ac.cy) ‡  
<sup>b</sup> Department of Chemistry, University of Florida, Gainesville, FL 32611-7200, USA. ‡  
<sup>c</sup> Department of Chemistry, University of Patras, 26500 Patras, Greece.  
 † Electronic Supplementary Information (ESI) available:  
<sup>95</sup> Crystallographic data (CIF format) for **1** and **2**·2py·3.6MeCN, synthetic details, bond valence sum calculations and various structural and magnetism figures. CCDC reference numbers 996832 and 996833 for **1** and **2**·2py·3.6MeCN, respectively. See DOI: 10.1039/b000000x/  
 ‡ Crystal data for **1**:  $\text{C}_{68}\text{H}_{140}\text{Mn}_{24}\text{O}_{84}\text{Ni}_2$ ,  $M_w = 3737.75$ , triclinic,  $a = 11.5790(6)$  Å,  $b = 16.5380(5)$  Å,  $c = 20.8160(8)$  Å,  $\alpha = 104.530(3)^\circ$ ,  $\beta = 105.960(4)^\circ$ ,  $\gamma = 102.440(2)^\circ$ ,  $V = 3532.5(3)$  Å<sup>3</sup>,  $T = 100(2)$  K, space group  $P\bar{1}$ ,  $Z = 1$ ,  $\rho_{\text{calcd}} = 1.757$  g cm<sup>-3</sup>, 25598 reflections collected, 12422 reflections used,  $R_1 [I > 2\sigma(I)] = 0.0555$ ,  $wR_2 = 0.1607$ . The asymmetric unit also contains severely disordered solvent molecules that could not be modeled properly. Thus, the SQUEEZE program was used to eliminate the contribution of the electron density in the disordered solvent region from the overall intensity data.

Crystal data for 2·2py·3.6MeCN: C<sub>121.20</sub>H<sub>213.80</sub>Mn<sub>15</sub>N<sub>9.60</sub>O<sub>50</sub>, Mw=3429.72, triclinic, a = 14.6777(2) Å, b = 15.9353(2) Å, c = 18.1069(2) Å, α = 72.526 (2)°, β = 86.197(2)°, γ = 84.174(2)°, V = 4015.9 (1) Å<sup>3</sup>, T = 100(2) K, space group P<sub>1</sub>, Z = 1, ρ<sub>calcd</sub> = 1.418 g cm<sup>-3</sup>, 65809 reflections collected, 18343 reflections used, R<sub>1</sub> [I > 2σ(I)] = 0.0486, wR<sub>2</sub> = 0.1219.  
Current address of MJM: Department of Chemistry, University of Ioannina, 45110, Ioannina, Greece.  
Current address of TCS: Department of Chemistry, Brock University St. Catharines, Ontario, L2S 3A1, Canada.

- 10  
1 (a) G. Aromi and E. K. Brechin, *Struct. Bond.*, 2006, **122**, 1; (b) A. J. Tasiopoulos and S. P. Perlepes, *Dalton Trans.*, 2008, 5537; (c) E. K. Brechin, *Chem. Commun.*, 2005, 5141; (d) G. Christou, *Polyhedron*, 2005, **24**, 2065.
- 15 2 (a) R. Bagai and G. Christou, *Chem. Soc. Rev.*, 2009, **38**, 1011; (b) D. Gatteschi and R. Sessoli, *Angew. Chem., Int. Ed.*, 2003, **42**, 268.
- 3 D. Gatteschi, R. Sessoli and J. Villain, *Molecular Nanomagnets*, Oxford University Press, New York, 2006.
- 4 (a) S. Zartilas, C. Papatriantafyllopoulou, T. C. Stamatatos, V. Nastopoulos, E. Cremades, E. Ruiz, G. Christou, C. Lampropoulos and A. J. Tasiopoulos, *Inorg. Chem.*, 2013, **52**, 12070; (b) M. Manoli, R. Inglis, M. J. Manos, V. Nastopoulos, W. Wernsdorfer, E. K. Brechin and A. J. Tasiopoulos, *Angew. Chem. Int. Ed.*, 2011, **50**, 4441; (c) A. J. Tasiopoulos, A. Vinslava, W. Wernsdorfer, K. A. Abboud and G. Christou, *Angew. Chem. Int. Ed.*, 2004, **43**, 2117; (d) G. A. Timco, T. B. Faust, F. Tuna and R. E. P. Winpenny, *Chem. Soc. Rev.* 2011, **40**, 3067, and references therein; (e) M. Manoli, A. Prescimone, R. Bagai, A. Mishra, M. Murugesu, S. Parsons, W. Wernsdorfer, G. Christou and E. K. Brechin, *Inorg. Chem.* 2007, **46**, 6968.
- 20 5 (a) S. T. Meally, G. Karotsis, E. K. Brechin, G. S. Papaefstathiou, P. W. Dunne, P. McArdle and L. F. Jones, *Cryst. Eng. Comm.*, 2010, **12**, 59; (b) T. C. Stamatatos, D. Foguet-Albiol, K. M. Poole, W. Wernsdorfer, K. A. Abboud, T. A. O'Brien, and G. Christou, *Inorg. Chem.*, 2009, **48**, 9831; (c) A. Ferguson, A. Parkin, J. Sanchez-Benitez, K. Kamenev, W. Wernsdorfer and M. Murrie, *Chem. Commun.*, 2007 3473; (d) J. T. Brockman, J. C. Huffman and G. Christou, *Angew. Chem. Int. Ed.*, 2002, **41**, 2506; (e) B. B. Bassil, M. Ibrahim, R. Al-Oweini, M. Asano, Z. Wang, J. van Tol, N. S. Dalal, K.-Y. Choi, R. N. Biboum, B. Keita, L. Nadjio and U. Kortz, *Angew. Chem. Int. Ed.*, 2011, **50**, 5961.
- 25 6 (a) L. K. Thompson, O. Waldmann and Z. Xu, *Coord. Chem. Rev.*, 2005, **249**, 2677; (b) L. Zhao, Z. Xu, L. K. Thompson and D. O. Miller, *Polyhedron*, 2001, **20**, 1359; (c) S. K. Dey, T. S. M. Abedin, L. N. Dawe, S. S. Tandon, J. L. Collins, L. K. Thompson, A. V. Postnikov, M. S. Allam and P. Muller, *Inorg. Chem.*, 2007, **46**, 7767; (d) L. N. Dawe, K. V. Shuvaev, L. K. Thompson, *Chem. Soc. Rev.*, 2009, **38**, 2334; (e) M. Ruben, J. Rojo, F. J. Romero-Salguero, L. H. Uppadine, J. -M. Lehn, *Angew. Chem. Int. Ed.*, 2004, **43**, 3644; (f) L. N. Dawe, K. V. Shuvaev, L. K. Thompson, *Inorg. Chem.*, 2009, **48**, 3323; (g) L. N. Dawe, T. S. M. Abedin, L. K. Thompson, *Dalton Trans.*, 2008, 1661.
- 30 7 (a) A. Chiolerio and D. Loss, *Phys. Rev. Lett.*, 1998, **80**, 169; (b) F. Meier and D. Loss, *Phys. Rev. B*, 2001, **64**, 224411; (c) F. Meier and D. Loss, *Phys. Rev. Lett.*, 2001, **86**, 5373. (d) O. Waldmann, T. C. Stamatatos, G. Christou, H. U. Gudel, I. Sheikin and H. Mutka, *Phys. Rev. Lett.*, 2009, **102**, 157202; (e) O. Cador, D. Gatteschi, R. Sessoli, A.-L. Barra, G. A. Timco and R. E. P. Winpenny, *J. Magn. Mater.*, 2005, **290**, 55.
- 35 8 O. Waldmann, *Coord. Chem. Rev.*, 2005, **249**, 2550.
- 9 (a) W. Liu and H.-H. Thorp, *Inorg. Chem.*, 1993, **32**, 4102; (b) I. D. Brown and D. Altermatt, *Acta Crystallogr., Sect. B*, 1985, 244.
- 40 10 (a) R. M. Bozorth, *J. Am. Chem. Soc.*, 1922, **44**, 2232; (b) G. Meyer, N. Gerlitzki, S. Hammerich, *Journal of Alloys and Compounds*, 2004, **380**, 71.
- 45 11 (a) M. Charalambous, E. E. Moushi, C. Papatriantafyllopoulou, W. Wernsdorfer, V. Nastopoulos, G. Christou and A. J. Tasiopoulos, *Chem. Commun.*, 2012, 5410; (b) W. -G. Wang, A. -J. Zhou, W. -X. Zhang, M. -L. Tong, X. -M. Chen, M. Nakano, C. C. Beedle and D. N. Hendrickson, *J. Am. Chem. Soc.*, 2007, **129**, 1014.
- 50  
55  
60  
65  
70