

## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)
Cite this: *Nanoscale*, 2024, **16**, 12492

# Ru doping and interface engineering synergistically boost the electrocatalytic performance of a WP/WP<sub>2</sub> nanosheet array for an efficient hydrogen evolution reaction†

 Zhichang Hu, Zhizhong Xiao, Wei Wei, Jian Yang, Xiaoyu Huang, Qingcheng Lu, Sundaram Chandrasekaran, Huidan Lu \* and Yongping Liu \*

The surface electronic structure and morphology of catalysts have a crucial impact on the electrocatalytic hydrogen evolution reaction performance. This work reports on the fabrication of a Ru-doped WP/WP<sub>2</sub> heterojunction nanosheet array electrode *via* a one-step phosphating treatment of a Ru-doped WO<sub>3</sub> precursor. Benefitting from the large electrochemical active surface of nanosheet arrays, rich WP/WP<sub>2</sub> heterojunction interface, and trace Ru atom doping, the catalyst has a fairly low overpotential of 58.0 mV at 10 mA cm<sup>-2</sup> and a Tafel slope of 50.71 mV dec<sup>-1</sup> in acid solution toward the electrocatalytic HER. Further, theoretical calculations unveil that Ru atom doping and interface effect synergistically optimized the electronic structure of the catalyst and hence weakened the adsorption capacity of the catalyst surface toward hydrogen (H), which lowered the Gibbs free energy ( $\Delta G_{H^+}$ ) and consequently effectively improved the HER performance. This work may open new avenues for developing advanced nanoarray electrodes with efficient electrochemical energy conversion.

Received 10th March 2024,

Accepted 3rd June 2024

DOI: 10.1039/d4nr01010h

[rsc.li/nanoscale](https://rsc.li/nanoscale)

## Introduction

Hydrogen (H<sub>2</sub>) is considered one of the ideal energy carriers most likely to replace traditional fossil energy because of its high energy density and clean and renewable characteristics.<sup>1,2</sup> Electrocatalytic water splitting provides an effective H<sub>2</sub> production method,<sup>3</sup> driven by the electric energy converted from clean and renewable energy, such as wind or solar energy.<sup>4,5</sup> To produce H<sub>2</sub> through electrocatalytic water splitting on a large scale, it is essential to obtain suitable catalyst materials with high catalytic performance and economical properties.<sup>6</sup> However, multi-active catalysts for electrocatalytic hydrogen evolution are mainly Pt series catalysts with scarce resources and high cost, significantly restricting their wide application.<sup>7</sup>

Transition-metal phosphides (TMPs) show numerous fascinating physical and chemical features, including high electronic conductivity, luminescence, thermoelectric, and catalytic characteristics, resulting from the unique characteristics of phosphorus atoms.<sup>8–10</sup> Tungsten phosphide is a suitable catalyst for electrocatalytic hydrogenation, whose catalytic

activity is higher than other tungsten compounds such as carbides, sulfides, and nitrides.<sup>11</sup> It has been stated in several reports that tungsten phosphide is highly active for electrocatalytic reactions and has low production costs.<sup>12–15</sup> However, bare WP or WP<sub>2</sub> show unsatisfactory HER overpotential. Thus, several groups used various methods to improve the HER activity. Wu *et al.*<sup>16</sup> prepared a coral-like WP nanorod array (C-WP/W), which had low overpotential (only 109 mV at 10 mA cm<sup>-2</sup>) and low Tafel slope (79.8 mV dec<sup>-1</sup>). The excellent electrocatalytic performance was attributed to its surface profile characterized by high structural stability and specific surface area. Liu *et al.*<sup>2</sup> synthesized an Ni-doped WP<sub>2</sub> nanosheet array, which achieved an overpotential of 109 mV (at a current density of 10 mA cm<sup>-2</sup>) and a Tafel slope of 65 mV dec<sup>-1</sup>. The high efficiency of the HER activity was attributed to its surface morphology and the improvement of the internal electronic structure of WP<sub>2</sub> *via* Ni doping. Thus, the fundamental catalytic advantages of phosphorus in WP is likely to arise from modifying the nature of tungsten.

In recent years, the construction of the heterojunction structure has been proven to be one of the effective ways to prepare high-efficiency electrocatalysts.<sup>17,18</sup> Abundant heterojunction interfaces are obtained through fine interface regulation, which leads to more catalytically active sites. Meanwhile, the charge transfer between the heterojunction interfaces can change the electronic structure of the two

Guangxi Key Laboratory of Electrochemical and Magneto-Chemical Functional Materials, College of Chemistry and Bioengineering, Guilin University of Technology, Guilin 541004, P. R. China. E-mail: [lhuidangl@163.com](mailto:lhuidangl@163.com), [liuyup624@163.com](mailto:liuyup624@163.com)

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4nr01010h>

phases, thereby adjusting the hydrogen adsorption energy.<sup>19,20</sup> Chen<sup>21</sup> obtained a unique eutectoid WC/W<sub>2</sub>C heterostructure by the calcination of two-dimensional organic–inorganic tungsten precursors. It represented excellent HER activity at a current density of 10 mA cm<sup>-2</sup>; the overpotential is only 75 mV, and the lower Tafel slope is 59 mV dec<sup>-1</sup>. Li<sup>22</sup> constructed a novel heterostructure composed of WP and Ni<sub>2</sub>P (WP/Ni<sub>2</sub>P P@NPC) as an efficient HER electrocatalyst. The catalyst had significant acid electrocatalytic activity for HER, with an overpotential of 157 mV and a current density of 10 mA cm<sup>-2</sup>. However, the HER performance of the catalyst currently obtained is still unable to achieve the level of commercial Pt/C. It is worth noting that Ru has been explored as a promising substitute for Pt electrocatalyst.<sup>23</sup> Ru is a noble metal, and the cost is relatively less than Pt, and the low-level use of Ru will greatly reduce the production cost. In this regard, Chen,<sup>24</sup> Liu,<sup>25</sup> Du<sup>26</sup> used low-level dopings of Ru on NiCoP, FeCoP, WC/WP, respectively, and they realized Pt-like HER. However, Ru with WP/WP<sub>2</sub> heterostructure is unexplored in energy conversion and storage. Therefore, it is worth trying and feasible to dope the appropriate proportional Ru into tungsten phosphide.

In this work, we prepared an Ru-doped WP/WP<sub>2</sub> nanosheet heterojunction array on carbon cloth (Ru-WP/WP<sub>2</sub> NH/CC) by the one-step phosphating treatment of the Ru-doped WO<sub>3</sub> (Ru-WO<sub>3</sub>/CC) precursor. The large electrochemical active surface of nanosheet arrays' morphology, tightly bounded WP/WP<sub>2</sub> heterojunction, and doping of Ru atom synergistically enhance the performance of electrocatalytic hydrogen evolution. This heterostructure exhibits Pt-like HER performance with a low overpotential of ~58.0 mV at a current density of 10 mA cm<sup>-2</sup> and a small Tafel slope value of ~47.98 mV dec<sup>-1</sup> in acidic electrolytes. We have discovered the phenomenon of local electronic enrichment in the heterogeneous structure by density functional theory (DFT). The doping of Ru optimizes the electronic system of WP/WP<sub>2</sub>, which rationally weakens the adsorption capacity of the catalyst surface to hydrogen (H). Thus, Ru-WP/WP<sub>2</sub> NH/CC exhibits the appropriate adsorption of Gibbs free energy ( $\Delta G_{H^+}$ ), and the effective HER performance is improved.

## Experimental

### Materials

Carbon cloth (CC, W0S1009) was purchased from Carbon Energy Technology Co., Ltd. Anhydrous tungsten hexachloride (WCl<sub>6</sub>, 99.9%) and sodium hypophosphite monohydrate (NaH<sub>2</sub>PO<sub>2</sub>·H<sub>2</sub>O, AR) were purchased from Mclean Biochemical Technology Co., Ltd. Anhydrous ethanol (CH<sub>3</sub>CH<sub>2</sub>OH, AR) and acetone (CH<sub>3</sub>COCH<sub>3</sub>, AR) were purchased from Guangdong Guanghua Technology Co., Ltd. Oxalic acid dihydrate (C<sub>2</sub>H<sub>2</sub>O<sub>4</sub>·2H<sub>2</sub>O, AR) were purchased from Sinopharm Chemical Reagent Co., Ltd. Anhydrous ruthenium trichloride (RuCl<sub>3</sub>, AR), platinum–carbon catalyst (20 wt% Pt/C), ruthenium oxide catalyst (RuO<sub>2</sub>, 98%), and Nafion reagent (5 wt%) were pur-

chased from Shanghai Aladdin Biochemical Technology Co., Ltd. All chemicals were used directly without any further purification.

### Synthesis of WO<sub>3</sub> and the Ru-WO<sub>3</sub> NS/CC precursor

The precursor Ru-WO<sub>3</sub> NS/CC was prepared by a simple solvothermal method. First, CC was put vertically into a 100 mL Teflon-lined stainless-steel autoclave, 50 mL nitric acid solution (volume ratio  $V_{\text{water}} : V_{\text{nitric acid}} = 20 : 30$  mL) was added, and subsequently it was sent into an oven for hydrophilic treatment at 100 °C for 10 h. After cooling, it was taken out and fully cleaned with deionized water, followed by ultrasonic washing with acetone, ethanol, and deionized water for 30 min, and dried in an oven at 60 °C for 12 h later use. A 100 mL Teflon-lined stainless-steel autoclave was prepared and the cleaned CC was placed vertically into it for later use. 40 mL of anhydrous ethanol was added to the Teflon-lined stainless-steel autoclave, and 0.3 g WCl<sub>6</sub>, 4.7 mg RuCl<sub>3</sub>, and 0.6 g of oxalate were dissolved in 40 mL of anhydrous ethanol. To eliminate the influence of air and dissolved oxygen, argon gas was used to remove the air for about 20–30 s, and the Teflon-autoclave was covered quickly. Then, the Teflon-lined stainless-steel autoclave was preheated in an oven at 60 °C for 30 min and subsequently reacted at 180 °C for 10 h. After cooling at room temperature, the sample was taken out, the surface was washed with anhydrous ethanol and dried. Finally, the sample was annealed at 500 °C for 2 h to obtain 3% Ru-WO<sub>3</sub> NS/CC. In addition, the doping amount of Ru in WO<sub>3</sub> nanosheets was controlled by changing the amount of RuCl<sub>3</sub> added during precursor synthesis. Samples with different Ru : W mole ratios of 0%, 0.1%, 0.5%, 1%, 3%, 5% and 7% were synthesized for concentration gradient optimization experiments.

### Synthesis of Ru-WP, Ru-WP<sub>2</sub> NS/CC, WP/WP<sub>2</sub>, and Ru-WP/WP<sub>2</sub> NH/CC

In a typical synthesis of Ru-WP/WP<sub>2</sub> NS/CC, the precursor was phosphatized *via* an *in situ* solid-state reaction. Generally, phosphating treatment was carried out in a tubular furnace with two-temperature controlled heating zones. The porcelain boat loaded with 4.0 g NaH<sub>2</sub>PO<sub>2</sub>·H<sub>2</sub>O was placed in the upstream heating zone and heated to 300 °C at a rate of 2.2 °C min<sup>-1</sup> and maintained for 2 h. On the other hand, the precursor sample placed in the lower half heating zone was heated to 700 °C at a ramping rate of 5 °C min<sup>-1</sup>; this temperature was maintained for 2 h. Ar gas flows at a rate of 20 s.c.c.m. (standard-state cubic centimeter per minute) as a protective atmosphere. After the reaction was completed and cooled to room temperature, the cathode electrocatalyst product Ru-WP/WP<sub>2</sub> NS/CC was obtained. By changing the phosphating temperature and keeping the other conditions the same, different products could be obtained. A phosphating temperature of 650 °C yields Ru-WP<sub>2</sub> NS/CC and 800 °C yields Ru-WP NS/CC.

### Physical characterization

The PANalytical X'Pert<sup>3</sup> diffractometer (Cu target,  $\lambda = 1.54056$  Å) was used to identify the crystal structure of the pre-

pared samples. The surface morphology and microstructure of catalyst materials were characterized by a SU5000 thermal field emission scanning electron microscope (SEM) and a JEM-2100F field emission transmission electron microscope (TEM). The surface chemical states and elemental chemical environments of the materials were analyzed by an ESCALAB 250Xi X-ray photoelectron spectrometer (XPS) with a monochromatic AlK $\alpha$  (1486.6 eV) line source.

### Electrochemical measurements

All electrochemical analyses were performed in a three-electrode cell for testing using an electrochemical workstation (CHI 760E, CH Instruments Inc.). The acid electrolyte was 0.5 M H<sub>2</sub>SO<sub>4</sub> for all the tests, a graphite rod was used as the counter electrode, Ag/AgCl (sat. KCl) electrode was used as the reference electrode, and a 1 × 1 cm<sup>2</sup> sample was used as the working electrode. During the HER test, the electrolyte was purged with N<sub>2</sub> gas for 30 min to eliminate the air interference. For the comparison study, the benchmark Pt/C (20 wt%) and RuO<sub>2</sub> catalysts were prepared on a 1 × 1 cm<sup>2</sup>-sized CC by a drop-casting method. In brief, 10 mg Pt/C (RuO<sub>2</sub>) catalyst was dispersed in a solution containing 230  $\mu$ L of anhydrous ethanol, 250  $\mu$ L of deionized water, and 20  $\mu$ L of 5% Nafion. Ultrasonic treatment was conducted for ~30 min to form a homogeneous catalyst ink. Then, 25  $\mu$ L (~0.5 mg cm<sup>-2</sup> loading, consistent with the average load of the catalyst samples grown on CC) catalyst ink drops were cast on the pre-treated CC and dried at room temperature. The cathodic linear scanning voltammetry (LSV) measurement scan range was 0.2 V to -0.6 V (vs. RHE), and the scan rate was 5 mV s<sup>-1</sup>. To eliminate the effect of the electrolyte ohmic resistance, *iR* correction ~95% was utilized. Finally, the measured potential was converted relative to RHE by the Nernst (eqn (1)).

$$E \text{ (vs. RHE)} = E \text{ (vs. Ag/AgCl)} + 0.197 \text{ V} + (0.0591 \times \text{pH}). \quad (1)$$

Electrochemical impedance spectroscopy (EIS) was performed to characterize the electrolyte resistance and capacitance of the electrocatalyst. The double-layer capacitance (*C*<sub>dl</sub>) of the catalyst was evaluated by cyclic voltammetry (CV) tests at different scanning rates (10–100 mV s<sup>-1</sup>). The electrochemical stability of the catalyst was assessed by conducting 2000 continuous CV cycles at a scanning rate of 100 mV s<sup>-1</sup>, followed by LSV tests. A continuous and stable overpotential with a current density of 10 mA cm<sup>-2</sup> for 86 000 s was conducted to test the electrochemical stabilities of the electrocatalyst.

### Computational methods

Density functional theory (DFT) was calculated using the CASTEP module of Material Studio 8.0. Based on XRD analysis and previous simulation reports,<sup>2,11,14,27</sup> we constructed two crystal faces with low surface energy, WP(011) and WP<sub>2</sub>(100), while the Layer tool was used to build the WP/WP<sub>2</sub> heterostructure model. Furthermore, to construct the Ru-doped WP/WP<sub>2</sub> system, one W atom in the WP/WP<sub>2</sub> system was replaced

by one Ru atom. For the initial cell structure optimization calculation of each model, 3 × 3 × 3 Monkhorst-Pack grid *k*-point was used to optimize the structure. In comparison, the adsorption H single-point energy and electronic structure were calculated by the 3 × 3 × 1 Monkhorst-Pack grid *k*-point. The Perdew–Burke–Ernzerhof (PBE) method of the Generalized Gradient Approximation (GGA) functional describes the electron exchange–correlation energy. Ultra-soft pseudopotentials were used to describe the electronic structure and interaction of the model more accurately. At the same time, the DFT-D of the Grimme method was applied for dispersion correction, spin polarization, and Broyden–Fletcher–Goldfarb–Shanno (BFGS) were set as the minimization algorithms for all calculations. The adsorption free energy of H on the catalyst surface  $\Delta G_{H^*}$  can be calculated by the following formula (2).<sup>28,29</sup>

$$\Delta G_{H^*} = \Delta E_{H^*} + \Delta ZPE - T\Delta S \quad (2)$$

among them,  $\Delta E_{H^*}$ ,  $\Delta ZPE$ , and  $T\Delta S$  represent the binding energy of adsorbate H on the surface of the catalyst, the zero-energy between the adsorption state and the gas phase, and the entropy change ( $T = 298$  K), respectively.  $\Delta ZPE - T\Delta S$  can be approximated to 0.24 eV.<sup>30,31</sup>  $\Delta E_{H^*}$  can be obtained from the following formula (3).

$$\Delta E_{H^*} = E_{H^*+\text{surface}} - E_{\text{surface}} - 1/2E_{H_2} \quad (3)$$

where  $E_{H^*+\text{surface}}$  and  $E_{\text{surface}}$  represent the total energy of the model after H adsorption and blank, respectively, and  $E_{H_2}$  represents the total energy of H<sub>2</sub> molecules in the gas phase. Therefore, the expression formula of H adsorption Gibbs free energy is  $\Delta G_{H^*} = \Delta E_{H^*} + 0.24$  eV.

## Results and discussion

The synthesis process of the nanosheet heterostructure catalyst material is shown in Fig. 1. Ru-WP/WP<sub>2</sub> NH/CC was synthesized by a two-step method: Ru-WO<sub>3</sub> was grown on CC by the solvothermal method, and then Ru-WP/WP<sub>2</sub> NH/CC was synthesized by *in situ* solid-phase phosphating.

Fig. 2(a, b) and Fig. S1† show the SEM images of Ru-WO<sub>3</sub> on CC at different magnification rates. The WO<sub>3</sub> nanosheets with about 30 nm thickness were vertically grown and interlaced with each other on the carbon cloth. After *in situ* phosphating at 700 °C for 2 h, as shown in Fig. 2(c, d) and Fig. S2,† the heterostructure of Ru-WP/WP<sub>2</sub> nanosheets maintained the basic nanosheet morphology. It is worth noting that many zigzag nanoparticles appeared on the edge of the nanosheet, and some micropores appeared in the interior of the nanosheets, which were beneficial for exposing more active sites to facilitate the catalytic hydrogen evolution reaction. EDS mappings were used to identify the elements in the catalyst. Fig. 2(e–h) and Fig. S3† show the composition and distribution of features in Ru-WP/WP<sub>2</sub> NH/CC, indicating that W, P, and trace Ru (0.5 at%) elements are uniformly distributed in the catalyst. As shown in Fig. 2(i) and (j), the HR-TEM images of the Ru-WP/WP<sub>2</sub> NH/CC samples showed clear lattice fringes

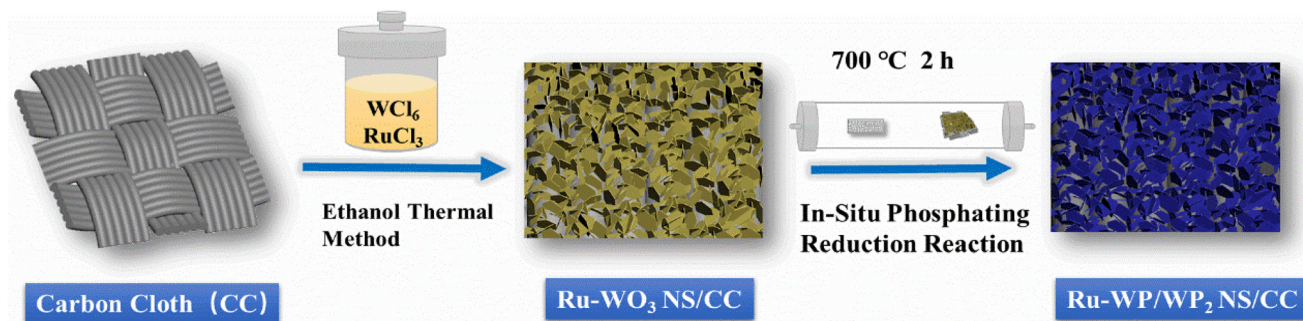


Fig. 1 Schematic illustration of the fabrication of Ru-WP/WP<sub>2</sub> NH/CC.


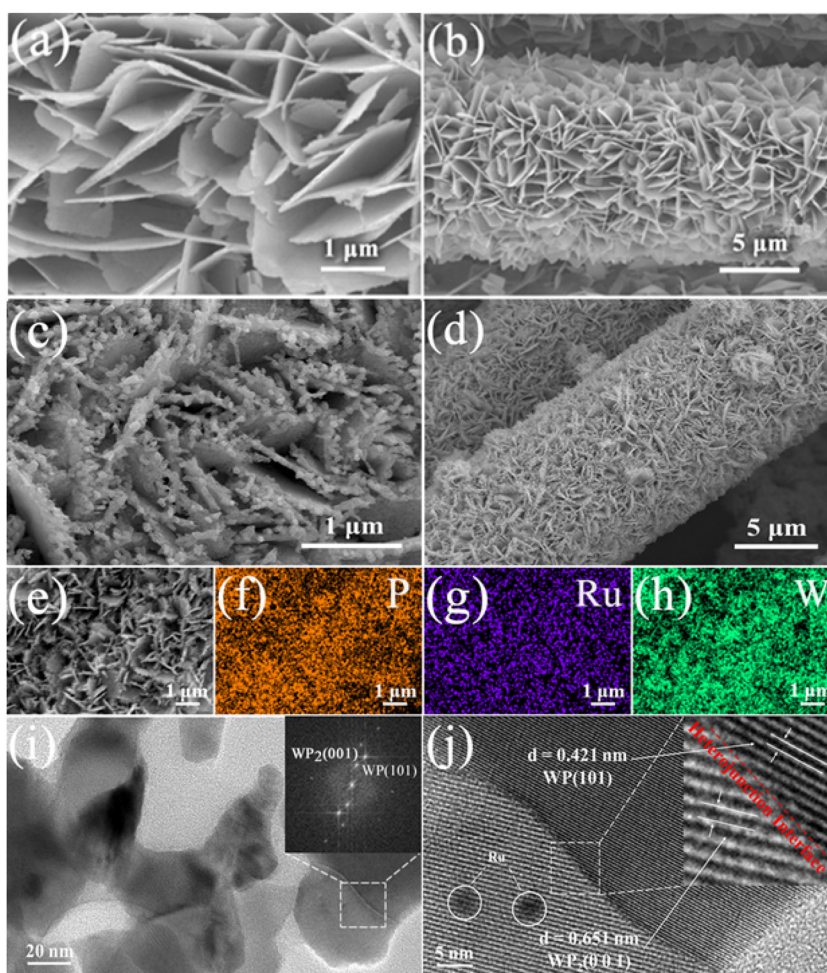


Fig. 2 SEM images of (a and b) Ru-WO<sub>3</sub> NH/CC and (c and d) WP/WP<sub>2</sub> NH/CC samples with different magnifications. (e–h) EDS elemental mapping analysis of P, W, and Ru in the Ru-WP/WP<sub>2</sub> NH/CC sample. (i and j) HR-TEM images of Ru-WP/WP<sub>2</sub> NH/CC.

with a lattice spacing of 0.421 and 0.651 nm, corresponding to the (101) and (001) crystal planes of WP and WP<sub>2</sub>, respectively, and showed obvious nanosheet heterostructure interface, indicating that the WP/WP<sub>2</sub> nanosheet heterostructure was successfully synthesized. In addition, the electron diffraction points of the heterojunction interface region of Ru-WP/WP<sub>2</sub> NH/CC can be obtained from the TEM characterization results,

such as the illustration shown in Fig. 2(g). The spots represent the crystal planes of WP and WP<sub>2</sub>, respectively, indicating that it is a heterojunction with two phases simultaneously.

Fig. 3 shows the X-ray diffraction (XRD) pattern and X-ray photoelectron spectroscopy (XPS) of the samples. As can be seen from Fig. 3(a), the diffraction peaks located at 20.97, 26.11, 31.10, 36.10, 43.95, and 46.60 were indexed to monocli-

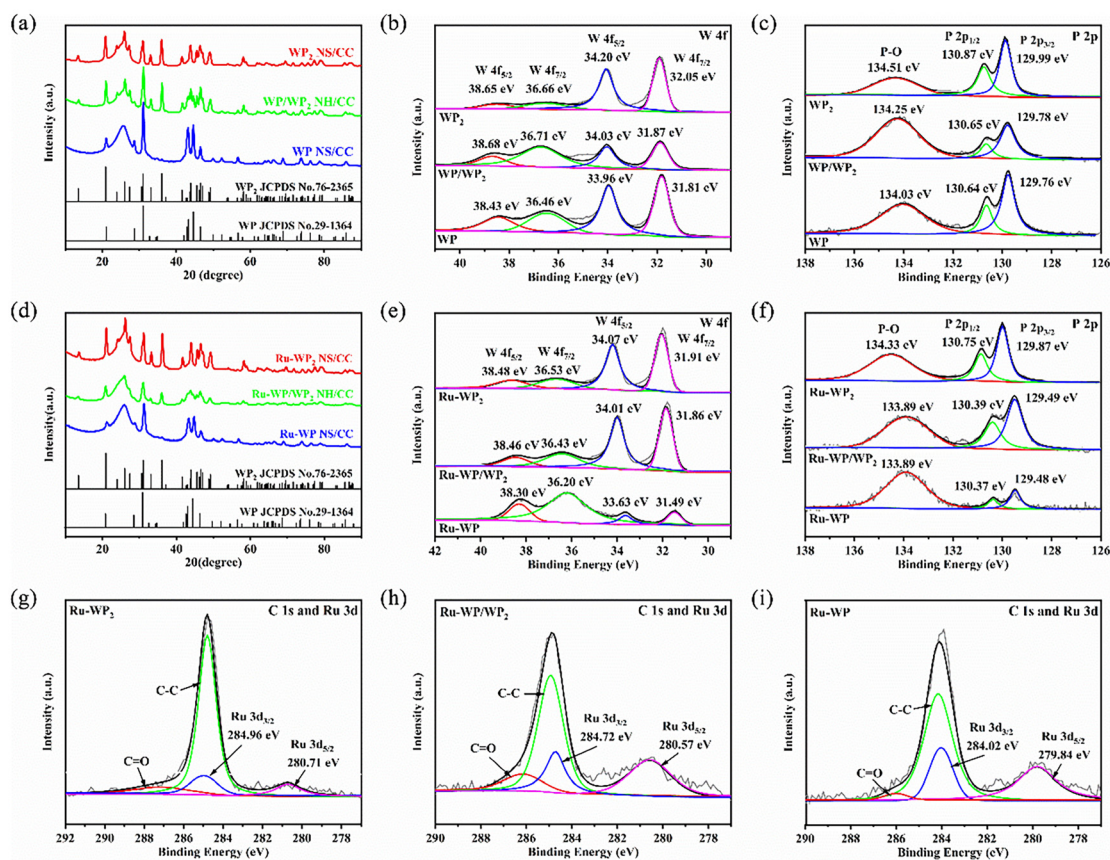

**Fig. 3** (a) XRD patterns of  $WP_2$  and  $WP/WP_2$  WP nanosheet arrays. XPS spectra of (b) W 4f and (c) P 2p of  $WP_2$  and  $WP/WP_2$  WP nanosheet arrays. (d) XRD patterns of Ru- $WP_2$ , Ru- $WP/WP_2$  and Ru-WP nanosheet arrays. XPS spectra of (e) W 4f, (f) P 2p, (g–i) C 1s and Ru 3d of Ru- $WP_2$ , Ru- $WP/WP_2$  and Ru-WP nanosheet arrays.

nic  $WP_2$  (JCPDS no. 76-2365), and the peaks appearing at 21.06, 28.66, 31.04, 42.86, 43.20, 44.58, and 46.50 were attributed to orthorhombic WP (JCPDS no. 29-1364). These peaks were all observed in  $WP/WP_2$  NH/CC, confirming that the heterojunction is composed of two substrates, namely, monoclinic  $WP_2$  and orthorhombic WP. The broad peaks with  $2\theta$  of  $26^\circ$  and  $43^\circ$  were attributed to carbon cloth (Fig. S4c†).<sup>32</sup> The XRD pattern of the heterojunction doped with Ru is shown in Fig. 3(d). The diffraction peaks of doped Ru are entirely consistent with the diffraction peaks of the undoped one, indicating that a trace amount of Ru doping has little effect on the lattice parameters of WP and  $WP_2$ . Notably, as shown in Fig. S4(a)†, products with different structures can be obtained by controlling different phosphating temperatures. At 550 and 600 °C, the mixed-phase of  $WO_3$  and  $WP_2$  is obtained, and when the temperature rises to 650 °C, the monoclinic  $WP_2$  phase is obtained and continues to increase to 800 °C; only the WP single phase is obtained. While phosphating at 700–750 °C, the result is the mixed-phase of WP and  $WP_2$ , namely, the  $WP/WP_2$  nanosheet heterostructure.


The bonding composition and chemical environment of chemical elements on the surface of the samples can be further analyzed by XPS. From the XPS core-level spectra

measurement in the ESI Fig. S5,† it can be seen that there are Ru, W, and P elements in the Ru- $WP/WP_2$  catalyst. As shown in Fig. 3(e), the  $WP/WP_2$  nanosheet heterostructure doped with Ru shows the binding energies (BEs) of W  $4f_{5/2}$  (34.01 eV) and W  $4f_{7/2}$  (31.86 eV) assigned to W–P in  $WP_2$  (WP).<sup>33,34</sup> Meanwhile, the deconvoluted peaks at 38.46 eV and 36.43 eV can be associated with the binding peaks of the  $4f_{5/2}$  and  $4f_{7/2}$  spectra, respectively, caused by the unavoidable air oxidation on the surface of the nanosheet heterostructure, which is very similar to the previous report.<sup>35,36</sup> Fig. 3(f) shows the P 2p energy spectrum, which produces two peaks at BEs of 130.39 eV and 129.49 eV corresponding to P  $2p_{1/2}$  and P  $2p_{3/2}$  satellite features generated by the WP bond in  $WP_2$  (WP), respectively.<sup>37</sup> In addition, the large and broad peak of BEs at 133.89 eV is the P–O bond caused by the oxidation of P atoms on the surface of the nanosheet material exposed to air.<sup>38</sup> As shown in Fig. 3(g–i), the deconvoluted Ru 3d spectra of Ru- $WP/WP_2$  NH/CC gave rise to the peaks at 284.72 and 280.57 eV due to the Ru  $3d_{3/2}$  and Ru  $3d_{5/2}$  states of metallic  $Ru^{4+}$  and  $Ru^0$ , respectively.<sup>7,39,40</sup> By comparing the XPS measurement spectrum of Fig. 3(b, c) and (e, f) with the catalyst doped with a low content of Ru, the binding energy of W and P moves slightly to a lower binding energy, which indicates that the part of the

electrons of Ru are transferred to W or P, and a small number of electrons are trapped by W and P.<sup>41</sup> It may be that the strong electron action of Ru promotes the excitation of active sites in the catalyst, which is beneficial to the HER process. In addition, with the increase in the phosphating temperature, the catalyst will change from  $WP_2$  to  $WP/WP_2$  and finally to WP. The chemical valence of W and Ru becomes lower, and the binding energy decreases in XPS analysis.<sup>42,43</sup>

To further prove the effects of the heterostructure and metal Ru doping on the catalyst's performance, we evaluated the HER activity of the samples in an acidic medium in a three-electrode device. As shown in the polarization curves of

Fig. 4(a), the Ru-WP/ $WP_2$  NH/CC synthesized under the optimal conditions suggested better electrocatalytic hydrogen evolution performance than the bare counterparts, Ru-doped single-phase WP or  $WP_2$ , and the polarization curve showed a linear sagging trend similar to that of the Pt/C catalyst. The overpotential is only 58.0 mV at a current density of 10  $\text{mA cm}^{-2}$ , and a high current density of 100  $\text{mA cm}^{-2}$  and 300  $\text{mA cm}^{-2}$  can be achieved when the overpotential is 113.7 mV and 166.3 mV, respectively. The lower overpotential means that the reaction activation energy barrier of the HER process is smaller, which is more dominant in the thermodynamic conversion efficiency. The overpotentials of Ru-WP NS/CC and Ru-

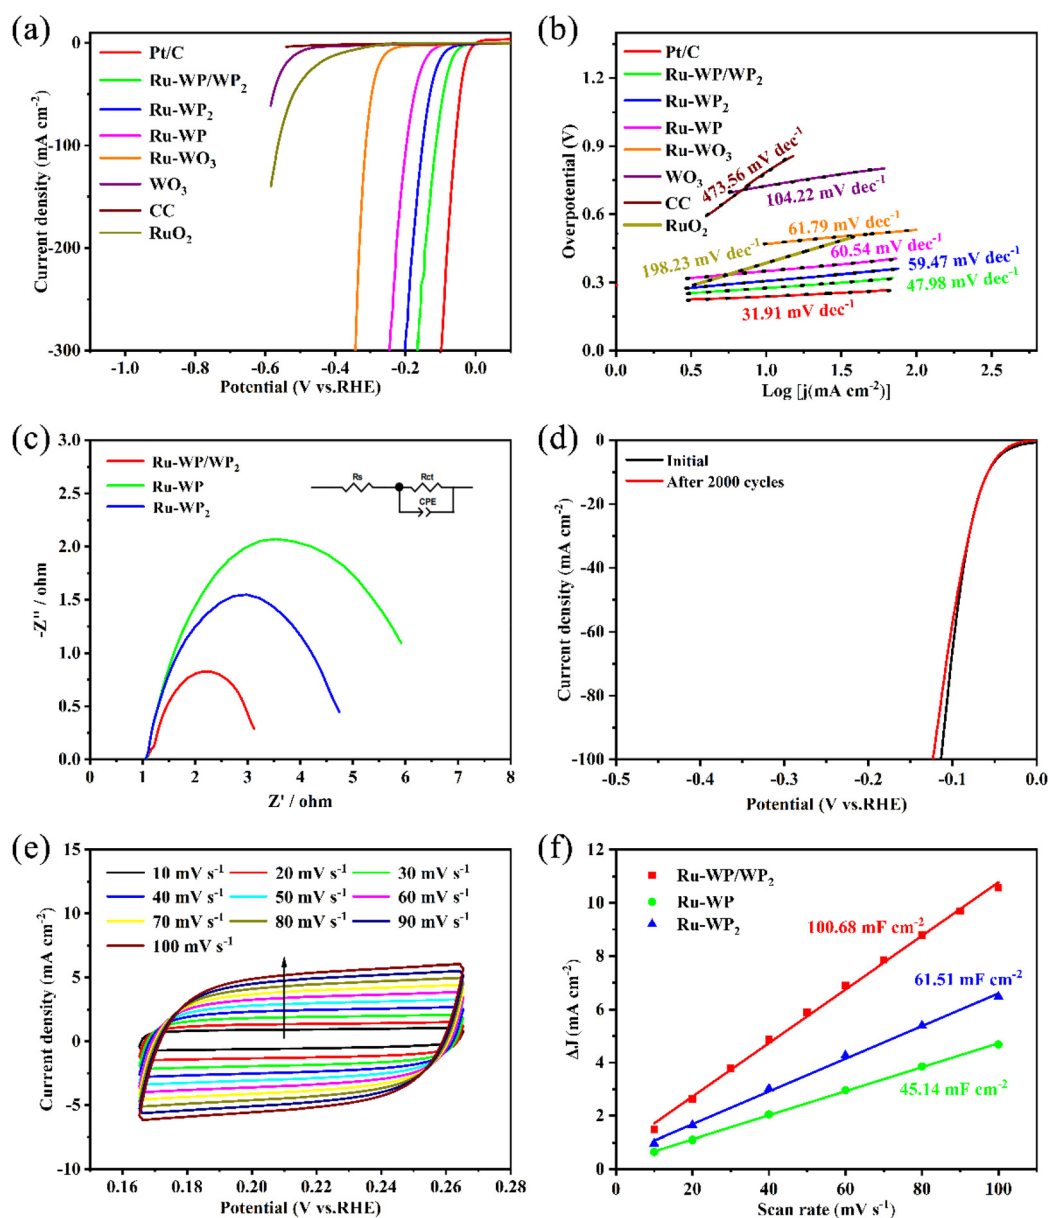


**Fig. 4** Evaluation of the electrocatalytic hydrogen evolution activity of the catalyst in 0.5 M  $H_2SO_4$ . (a) Linear sweep voltammetry curves of the catalysts at a scanning rate of 5  $\text{mV s}^{-1}$ . (b) Tafel slope plots. (c) Nyquist fitting curves. (d) HER durability test. Polarization curve after 2000 cyclic voltammetry scans. (e) Cyclic voltammetry curves at different scanning rates (10–100  $\text{mV s}^{-1}$ ). (f) The double-layer capacitance of the catalyst was calculated on the basis of the cyclic voltammetry curve.

WP<sub>2</sub> NS/CC were 131.2 mV and 89.1 mV at a current density of 10 mA cm<sup>-2</sup>, respectively. Tafel slope is an important parameter for evaluating the reaction kinetics in the HER process.<sup>44</sup> As shown in Fig. 4(b), the Ru-WP/WP<sub>2</sub> NH/CC sample exhibits a small Tafel slope (47.98 mV dec<sup>-1</sup>) close to that of the Pt/C catalyst (31.91 mV dec<sup>-1</sup>), which represents efficient HER activation reaction rate and fast electron transport kinetics, manifesting that the rate-determining step of the catalyst is possibly determined by the Volmer–Heyrovsky pathway.<sup>45</sup> Ru-WP NS/CC (60.54 mV dec<sup>-1</sup>) and Ru-WP<sub>2</sub> NS/CC (59.47 mV dec<sup>-1</sup>), Ru-WP/WP<sub>2</sub> nanosheet heterostructures still maintain fascinating electrocatalytic hydrogen evolution properties, suggesting the importance of the heterostructure structure. In addition, we optimized the Ru concentration gradient and phosphating temperature gradient of synthetic catalyst materials. From the concentration gradient optimization (ESI Table S1†), it can be known that when Ru is added to the preparation precursor, Ru : W is 0.1%, 0.5%, 1%, 3%, 5%, and 7%, and the overpotential of Ru-WP/WP<sub>2</sub> NH/CC is 184.7 mV, 180.7 mV, 131.1 mV, 58.0 mV, 94.7 mV, and 100.4 mV, respectively, at a current density of 10 mA cm<sup>-2</sup>. This shows that the optimal molar ratio of Ru : W is about 3%. At the same time, the temperature gradient optimization (Table S2†) shows that the performance of the catalyst material obtained at 700 °C is the best. The lower temperature cannot completely phosphatize to form a WO<sub>3</sub>/WP<sub>2</sub> mixed-phase catalyst. At the same time, the too high temperature will destroy the surface morphology of the original tungsten trioxide catalyst nanosheet array and form relatively low HER activities of WP. Table S3† summarizes the reports of similar catalysts in recent years. In contrast, Ru-WP/WP<sub>2</sub> NH/CC still exposes relatively pre-eminent HER behavior.

The charge transfer resistance ( $R_{ct}$ ) of the sample was analyzed by electrochemical impedance spectroscopy (EIS), such as the Nyquist diagram of Fig. 4(c), and the kinetic process of the polarization reaction was further studied. The equivalent circuit model is shown in the illustration of Fig. 4(c), where  $R_s$  and  $R_{ct}$  are the electrolyte resistance and charge transfer resistance of the working electrode, respectively, and the CPE is generated by the constant phase element of the working electrode. Under the applied bias voltage corresponding to 10 mA cm<sup>-2</sup> current density, compared with single-phase Ru-doped WP or WP<sub>2</sub>, the  $R_{ct}$  of Ru-WP/WP<sub>2</sub> NH/CC is only 2.20 Ω ( $R_{ct}$  of Ru-WP NS/CC is 4.22 Ω and  $R_{ct}$  of Ru-WP<sub>2</sub> NS/CC is 5.20 Ω), which shows higher charge transfer efficiency and electron transfer kinetics for HER. We further studied the charge transfer resistance of the catalyst materials with different Ru doping amounts and phosphating temperatures, as shown in Fig. S9(a) and (b).† It was proved that an appropriate concentration of Ru doping, the heterostructure can effectively reduce the charge transfer resistance. The stability of Ru-WP/WP<sub>2</sub> NH/CC is also studied by long-term durability. As shown in Fig. 4(d), the polarization curves of the catalyst display no noticeable change before and after 2000 cycles of continuous CV tests, which shows the excellent electrochemical stability of Ru-WP/WP<sub>2</sub> NH/CC. As shown in Fig. S10,† we tested the XRD

pattern of the catalyst before and after HER and found that only the crystal peak value decreased. Fig. S11† shows the time-dependent current density curve of 3% Ru-WP/WP<sub>2</sub>, and the catalyst maintained a constant current density of 10 mA cm<sup>-2</sup> catalytic activity for at least 86 000 s, implying that it has high stability in acidic electrolyte. For comparison, we provide stability tests for RuO<sub>2</sub>,<sup>46,47</sup> as shown in Fig. S12.† In order to evaluate the electrochemically activity surface area (ECSA) of the catalyst, we collected the CV curve with the scanning rate of 10–100 mV s<sup>-1</sup> and estimated the electrical double-layer capacitance ( $C_{dl}$ ) by taking the non-Faraday region. Fig. 4(f) shows the double layer capacitance fitting line of the catalyst. Ru-WP/WP<sub>2</sub> NH/CC has a potential of 0.21 V (vs. RHE) corresponding to the current density; the calculated  $C_{dl}$  is 100.68 mF cm<sup>-2</sup>, while the  $C_{dl}$  of Ru-WP NS/CC and Ru-WP<sub>2</sub> NS/CC is 45.14 mF cm<sup>-2</sup> and 61.51 mF cm<sup>-2</sup>, respectively. We further studied the TOF curves of different catalysts, which are shown in Fig. S13.† The results show that the Ru-WP/WP<sub>2</sub> nanosheet heterostructure has an excellent electrochemically activity surface area, which is higher than that of the Ru-WP and Ru-WP<sub>2</sub> nanosheet arrays. This is attributed to the WP/WP<sub>2</sub> heterostructure composite phase having a rich phase interface than single-phase WP or WP<sub>2</sub>, which provides more new active sites resulting from the interfacial effect. At the same time, Ru atoms doping into the host lattice reduced the energy barrier of the HER reaction and improved the electrochemical activity. In additional, the nanosheet heterostructure itself has a wide specific surface area, which enables the fast mass and ions transfer during the reactions.

The Gibbs free energy of hydrogen adsorption ( $\Delta G_{H^*}$ ) is one of the important indexes to evaluate the HER performance. When  $\Delta G_{H^*}$  is close to 0, it is considered the ideal electrocatalyst for HER.<sup>48,49</sup> We used density functional theory (DFT) to evaluate the  $\Delta G_{H^*}$  and electronic structure changes of the Ru-doped WP/WP<sub>2</sub> nanosheet heterostructure. Fig. 5(a) shows the models of Ru-WP/WP<sub>2</sub> employed in the calculation after geometry optimization. The Gibbs free energy of the catalyst at different hydrogen adsorption sites was evaluated. According to the calculation results and comparison data in Table S4,† the representative metal W site with H adsorption energy closer to 0 was finally selected as the hydrogen adsorption site. Moreover, Fig. S15 and S17† were demonstrated as the hydrogen adsorption models of Ru-WP/WP<sub>2</sub> and WP/WP<sub>2</sub> heterostructure after structural optimization. Fig. S19, S21, S23, and S25† exhibit the hydrogen adsorption models of Ru-WP<sub>2</sub>, WP<sub>2</sub>, Ru-WP, and WP, respectively, after structural optimization. It is worth noting that the unilateral WP and WP<sub>2</sub> models in the heterostructure structure are only inconsistent with the WP and WP<sub>2</sub> models in the number of extended supercells. In addition, we compared the effects of different replacement sites of Ru in the heterostructure structure on the Gibbs free energy of hydrogen adsorption, and detailed data are summarized in ESI Table S5.† As Fig. 5(b) shows the Gibbs free energy diagrams of Ru-WP/WP<sub>2</sub>, WP/WP<sub>2</sub>, Ru-WP<sub>2</sub>, WP<sub>2</sub>, Ru-WP and WP models, depicting the free energy barrier of H adsorption and desorption on the catalyst surface. As shown in Fig. 5(b)

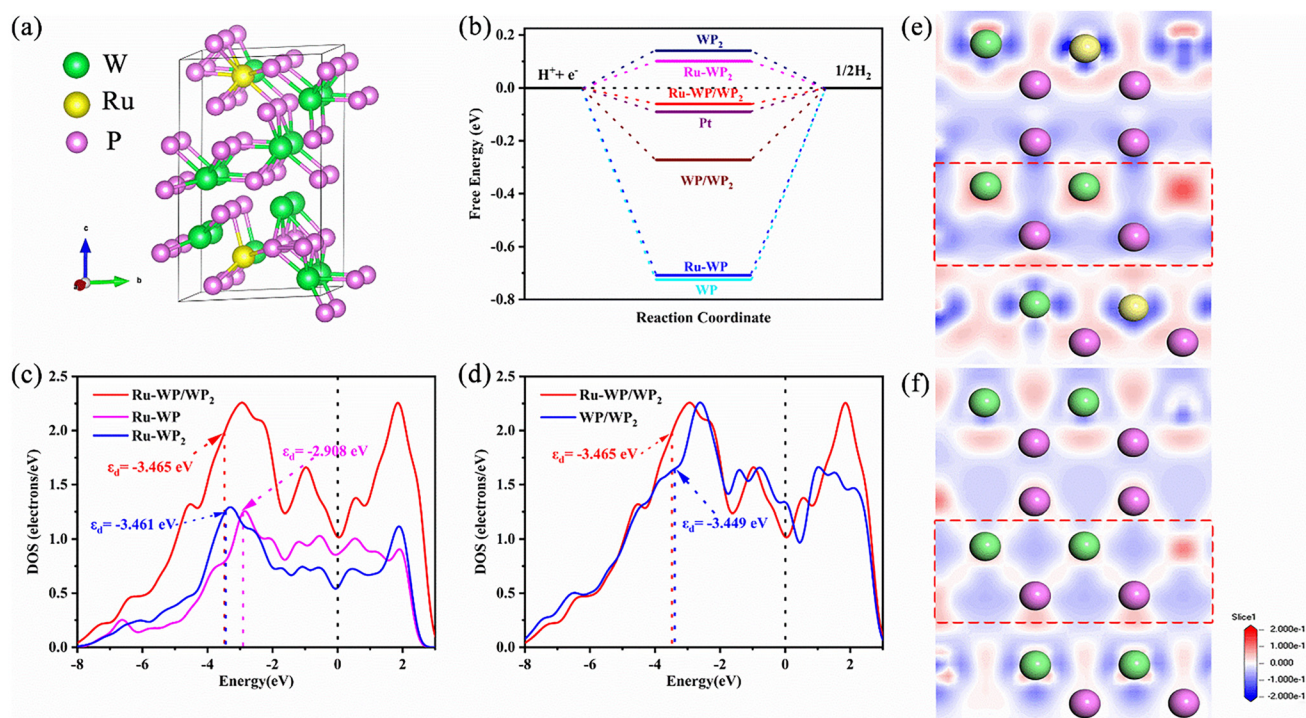

**Fig. 5** (a) Views of the structure model for Ru-WP/WP<sub>2</sub>. (b) Gibbs free energy diagram was calculated for different catalyst materials. (c and d) d-Orbital Skewness Density (d-DOS) diagrams of W atoms at the adsorption site. The black dotted line (0 eV) indicates the position of the Fermi level, and the other dotted lines represent the d-band center corresponding to each electrocatalyst material. (e) Ru-WP/WP<sub>2</sub> and (f) WP/WP<sub>2</sub> of charge density difference diagram. Among them, red represents electron accumulation, and blue represents electron consumption. Yellow is the Ru atom, green is the W atom, and pink is the P atom. The red dashed box shows the heterostructure interface and interface atoms.

and Table S4,<sup>†</sup> the  $\Delta G_{H^*}$  of Pt(111) is only  $-0.09$  eV, which is very close to the ideal  $\Delta G_{H^*} = 0$  eV, indicating that it has excellent HER performance. Similarly, the  $\Delta G_{H^*}$  value of the double-site Ru-doped double W-site adsorption (*i.e.*, both the WP side and the WP<sub>2</sub> side of the heterostructure are Ru-doped, and H is adsorbed on W) is very low  $-0.06$  eV, which is more consistent with the ideal Gibbs free energy of hydrogen evolution. Also, the  $\Delta G_{H^*}$  of Ru-WP and Ru-WP<sub>2</sub> are  $-0.71$  eV and  $-0.10$  eV, respectively. It has been proved that the construction of WP/WP<sub>2</sub> heterostructure can reduce the free energy barrier and make the  $\Delta G_{H^*}$  value closer to zero.

In addition, the  $\Delta G_{H^*}$  value of H adsorption on pure WP/WP<sub>2</sub> double W sites is  $-0.272$  eV, which indicates that metal Ru doping can also balance the competition between H adsorption and desorption processes, making the  $\Delta G_{H^*}$  value closer to zero, which will be a very favorable condition for HER. Generally speaking, a very high  $\Delta G_{H^*}$  value indicates that the adsorption capacity of H is relatively weak, which makes it difficult to adsorb H on the surface of the catalyst, which is not conducive to the occurrence of HER, while a very low  $\Delta G_{H^*}$  value means that H will be tightly adsorbed on the surface of the catalyst, which seriously limits the desorption of H and the precipitation of H<sub>2</sub>,<sup>50</sup> suggesting that Ru-WP/WP<sub>2</sub> NH/CC has outstanding HER activity. According to the d-band theory, the d-band center ( $\epsilon_d$ ) can effectively describe the binding strength between the adsorbed H and the catalyst surface.<sup>51</sup> As shown

in the partial density of states (d-DOS) diagram of the d orbital of the W atom at the adsorption site in Fig. 5(c) and (d), the d band center of Ru-WP/WP<sub>2</sub> is farther away from the Fermi level than Ru-WP, Ru-WP<sub>2</sub>, and WP/WP<sub>2</sub>. In general, a more negative band center weakens the binding between the adsorbent (H) and the catalyst's surface. For Ru-WP/WP<sub>2</sub>, it is beneficial to the desorption of H and the precipitation of H<sub>2</sub>. It also endows it with a  $\Delta G_{H^*}$  closer to the theoretical optimal value of 0. The distribution of local electrons and the difference in the electronic structure can be understood by calculating the differential charge density of each catalyst model. As can be seen from the differential charge density diagram in Fig. 5(e) and (f), compared with WP/WP<sub>2</sub>, there is a strong electron consumption behavior around the yellow Ru atom of Ru-WP/WP<sub>2</sub> NH/CC, indicating that Ru has lost electrons, which is consistent with the previous XPS test and the analysis results. The electron accumulation behavior of W atoms between the heterostructure interfaces occurs, which means that electrons transfer from Ru to heterostructure interfaces and gather around W atoms, which increases their electron density. Also, the P atom near Ru shows a state of partial electron aggregation, which may be related to Ru's strong electron dissipation behavior. In addition, the differential charge densities of monomer WP and monomer WP<sub>2</sub> and WP/WP<sub>2</sub> heterostructures are compared, and they are shown in Fig. S20, S22, S24, and S25.<sup>†</sup> When single-phase WP and WP<sub>2</sub> combine into

heterostructures, except for the interface atoms, the phenomenon of local loss of electrons around other metal atoms (Ru or W) no longer exists but is replaced by a darker blue, which means that the behavior of dispersed electrons is more obvious, indicating that there is a significant modulation behavior in the local charge distribution of the heterostructure interface. These results show that there is an ideal electronic structure in the heterostructure of the WP/WP<sub>2</sub> nanosheet, and after metal Ru doping, Ru as an electron donor provides more electrons to fill the interface, the heterostructure maintains a relatively electron-enriched state, and the adsorption capacity of H on the surface of the catalyst is reasonably regulated. Thus, a  $\Delta G_{H^+}$  value close to zero is obtained, which effectively reduces the energy barrier of the HER process. This is also the performance of Ru-WP/WP<sub>2</sub> NH/CC with high HER activity.

## Conclusions

In conclusion, through the strategy of *in situ* phosphating, a Ru-doped WP/WP<sub>2</sub> nanosheet heterostructure array (Ru-WP/WP<sub>2</sub> NH/CC) was grown on the surface of carbon cloth for the first time. As the electrocatalyst of a cathode, Ru-WP/WP<sub>2</sub> NH/CC shows excellent HER activities. In the acid electrolyte of 0.5 M H<sub>2</sub>SO<sub>4</sub>, the current density can reach 10 mA cm<sup>-2</sup> when the overpotential is only 58.0 mV, and the corresponding low Tafel slope is only 47.98 mV dec<sup>-1</sup>. The HER activities are attributed to the fact that the heterostructure of the catalyst nanosheet replicates the fascinating nanosheet morphology of the precursor and forms many closely bonded interfaces; in addition, the doping of trace Ru atoms improves the inherent electronic structure and obtains more HER active sites. The DFT calculation further shows that the WP/WP<sub>2</sub> of the heterostructure structure shows a favorable heterostructure interface. The doping of Ru optimizes the original electronic structure, which maintains the electron-enriched state of the heterostructure, weakens the binding ability between the adsorbent H and the catalyst surface, makes the hydrogen adsorption Gibbs free energy closer to the thermal median value 0, and enhances the HER activity. This work proposes a new strategy to improve the activity for electrocatalytic HER. It provides a valuable insight into the construction of reasonable heterostructure nanowires and the use of other atoms to regulate the electronic structure.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by the National Natural Science Foundation of China (22062005, 22165005, U20A20128, 52004076) and the Guangxi Science Fund for Distinguished Young Scholars (2019GXNSFFA245016).

## References

- 1 J. A. Turner, *Science*, 2004, **305**, 972–974.
- 2 W. Liu, P. Geng, S. Li, W. Liu, D. Fan, H. Lu, Z. Lu and Y. Liu, *J. Energy Chem.*, 2021, **55**, 17–24.
- 3 H. Li, M. Hu, L. Zhang, L. Huo, P. Jing, B. Liu, R. Gao, J. Zhang and B. Liu, *Adv. Funct. Mater.*, 2020, **30**, 2003198.
- 4 J. Lin, Y. Liu, Y. Liu, C. Huang, W. Liu, X. Mi, D. Fan, F. Fan, H. Lu and X. Chen, *ChemSusChem*, 2019, **12**, 961–967.
- 5 L. Shang, Y. Zhao, X.-Y. Kong, R. Shi, G. I. N. Waterhouse, L. Wen and T. Zhang, *Nano Energy*, 2020, **78**, 105375.
- 6 K. Jiang, B. Liu, M. Luo, S. Ning, M. Peng, Y. Zhao, Y. R. Lu, T. S. Chan, F. M. F. de Groot and Y. Tan, *Nat. Commun.*, 2019, **10**, 1743.
- 7 Y. Xu, S. Yin, C. Li, K. Deng, H. Xue, X. Li, H. Wang and L. Wang, *J. Mater. Chem. A*, 2018, **6**, 1376–1381.
- 8 H. Wang, Y. Guo, Q. Mao, H. Yu, K. Deng, Z. Wang, X. Li, Y. Xu and L. Wang, *Nanoscale*, 2023, **15**, 7765–7771.
- 9 H. Ma, W. Yan, Y. Yu, L. Deng, Z. Hong, L. Song and L. Li, *Nanoscale*, 2023, **15**, 1357–1364.
- 10 Y. C. Huang, Z. Y. Hu, L. A. Huang, Z. P. Wang, Z. P. Lin, S. J. Shen, W. W. Zhong and J. Q. Pan, *Nanoscale*, 2023, **15**, 3550–3559.
- 11 F. Meng, Y. Yu, D. Sun, L. Li, S. Lin, L. Huang, W. Chu, S. Ma and B. Xu, *Appl. Surf. Sci.*, 2021, **546**, 148926.
- 12 X. Lv, X. Li, C. Yang, X. Ding, Y. Zhang, Y. Z. Zheng, S. Li, X. Sun and X. Tao, *Adv. Funct. Mater.*, 2020, **30**, 1910830.
- 13 L. Yu, I. K. Mishra, Y. Xie, H. Zhou, J. Sun, J. Zhou, Y. Ni, D. Luo, F. Yu, Y. Yu, S. Chen and Z. Ren, *Nano Energy*, 2018, **53**, 492–500.
- 14 W. Liu, P. Geng, S. Li, R. Zhu, W. Liu, H. Lu, S. Chandrasekaran, Y. Pang, D. Fan and Y. Liu, *Int. J. Hydrogen Energy*, 2020, **45**, 28576–28585.
- 15 Z. Pu, X. Ya, I. S. Amiinu, Z. Tu, X. Liu, W. Li and S. Mu, *J. Mater. Chem. A*, 2016, **4**, 15327–15332.
- 16 L. Wu, Z. Pu, Z. Tu, I. S. Amiinu, S. Liu, P. Wang and S. Mu, *Chem. Eng. J.*, 2017, **327**, 705–712.
- 17 Q. Liu, Z. Xue, B. Jia, Q. Liu, K. Liu, Y. Lin, M. Liu, Y. Li and G. Li, *Small*, 2020, **16**, e2002482.
- 18 R. Zhang, G. Wang, Z. Wei, X. Teng, J. Wang, J. Miao, Y. Wang, F. Yang, X. Zhu, C. Chen, E. Zhou, W. Hu and X. Sun, *J. Mater. Chem. A*, 2021, **9**, 1221–1229.
- 19 Y. Du, H. Zhao, W. Wang, Y. Yang, M. Wang, S. Li, Y. Liu and L. Wang, *Dalton Trans.*, 2021, **50**, 391–397.
- 20 J. Wu, R. Zhao, H. Xiang, C. Yang, W. Zhong, C. Zhang, Q. Zhang, X. Li and N. Yang, *Appl. Catal., B*, 2021, **292**, 120200.
- 21 Z. Chen, W. Gong, S. Cong, Z. Wang, G. Song, T. Pan, X. Tang, J. Chen, W. Lu and Z. Zhao, *Nano Energy*, 2020, **68**, 104335.
- 22 T. Li, H. J. Chen, Z. H. Chen, Z. X. Xue, X. H. Zhang and B. Hui, *ACS Sustainable Chem. Eng.*, 2023, **11**, 14549–14558.
- 23 P. Li, W. Li, Y. Huang, J. Li, Q. Huang, S. Zhao and S. Tian, *Nanoscale*, 2022, **14**, 6258–6267.

- 24 D. Chen, R. Lu, Z. Pu, J. Zhu, H.-W. Li, F. Liu, S. Hu, X. Luo, J. Wu, Y. Zhao and S. Mu, *Appl. Catal., B*, 2020, **279**, 119396.
- 25 H. Liu, X. Li, L. Ge, C. Peng, L. Zhu, W. Zou, J. Chen, Q. Wu, Y. Zhang, H. Huang, J. Wang, Z. Cheng, Z. Fu and Y. Lu, *Catal. Sci. Technol.*, 2020, **10**, 8314–8324.
- 26 H. Du, Z. Du, T. Wang, S. He, K. Yang, K. Wang, L. Xie, W. Ai and W. Huang, *Sci. China Mater.*, 2022, **65**, 967–973.
- 27 M. Pi, T. Wu, D. Zhang, S. Chen and S. Wang, *Electrochim. Acta*, 2016, **216**, 304–311.
- 28 S. Chandrasekaran, P. Zhang, F. Peng, C. Bowen, J. Huo and L. Deng, *J. Mater. Chem. A*, 2019, **7**, 6161–6172.
- 29 D. Zhao, K. Sun, W. C. Cheong, L. Zheng, C. Zhang, S. Liu, X. Cao, K. Wu, Y. Pan, Z. Zhuang, B. Hu, D. Wang, Q. Peng, C. Chen and Y. Li, *Angew. Chem., Int. Ed.*, 2020, **59**, 8982–8990.
- 30 F. Yang, Y. Zhao, Y. Du, Y. Chen, G. Cheng, S. Chen and W. Luo, *Adv. Energy Mater.*, 2018, **8**, 1703489.
- 31 Q. Zhou, Z. Shen, C. Zhu, J. Li, Z. Ding, P. Wang, F. Pan, Z. Zhang, H. Ma, S. Wang and H. Zhang, *Adv. Mater.*, 2018, **30**, e1800140.
- 32 H. Yu, C. Zhu, K. Zhang, Y. Chen, C. Li, P. Gao, P. Yang and Q. Ouyang, *J. Mater. Chem. A*, 2014, **2**, 4551–4557.
- 33 M. Pi, T. Wu, D. Zhang, S. Chen and S. Wang, *Electrochim. Acta*, 2016, **216**, 304–311.
- 34 M. Pi, W. Guo, T. Wu, X. Wang, D. Zhang, S. Wang and S. Chen, *J. Power Sources*, 2017, **364**, 253–257.
- 35 B. Ren, D. Li, Q. Jin, H. Cui and C. Wang, *J. Mater. Chem. A*, 2017, **5**, 19072–19078.
- 36 S. S. Nkabinde, P. V. Mwonga, S. Mpelane, Z. B. Ndala, T. Kolokoto, N. P. Shumbula, O. Nchoe, R. R. Maphanga, K. I. Ozoemena, K. P. Mubiayi and N. Moloto, *New J. Chem.*, 2021, **45**, 15594–15606.
- 37 M. Pi, D. Zhang, S. Wang and S. Chen, *Mater. Lett.*, 2018, **213**, 315–318.
- 38 X.-D. Wang, Y.-F. Xu, H.-S. Rao, W.-J. Xu, H.-Y. Chen, W.-X. Zhang, D.-B. Kuang and C.-Y. Su, *Energy Environ. Sci.*, 2016, **9**, 1468–1475.
- 39 A. Maiti and S. K. Srivastava, *ACS Appl. Nano Mater.*, 2021, **4**, 7675–7685.
- 40 M. Yang, L. Jiao, H. Dong, L. Zhou, C. Teng, D. Yan, T.-N. Ye, X. Chen, Y. Liu and H.-L. Jiang, *Sci. Bull.*, 2021, **66**, 257–264.
- 41 M. Zhao, H. Li, W. Li, J. Li, L. Yi, W. Hu and C. M. Li, *Chem. – Eur. J.*, 2020, **26**, 17091–17096.
- 42 H. Zhu, Q. Yang, D. Liu, D. Liu, W. Zhang, Z. Chu, X. Wang, S. Yan, Z. Li and Z. Zou, *J. Phys. Chem. Lett.*, 2020, **11**, 9184–9194.
- 43 X. Zheng, P. Cui, Y. Qian, G. Zhao, X. Zheng, X. Xu, Z. Cheng, Y. Liu, S. X. Dou and W. Sun, *Angew. Chem., Int. Ed.*, 2020, **59**, 14533–14540.
- 44 Q. Gong, Y. Wang, Q. Hu, J. Zhou, R. Feng, P. N. Duchesne, P. Zhang, F. Chen, N. Han, Y. Li, C. Jin, Y. Li and S. T. Lee, *Nat. Commun.*, 2016, **7**, 13216.
- 45 Z. Huang, S. Yuan, T. Zhang, B. Cai, B. Xu, X. Lu, L. Fan, F. Dai and D. Sun, *Appl. Catal., B*, 2020, **272**, 118976.
- 46 D. Chen, H. Zhao, R. Yu, K. Yu, J. Zhu, J. Jiao, X. Mu, J. Yu, J. Wu and S. Mu, *Energy Environ. Sci.*, 2024, **17**, 1885–1893.
- 47 D. Chen, R. Yu, D. Wu, H. Zhao, P. Wang, J. Zhu, P. Ji, Z. Pu, L. Chen, J. Yu and S. Mu, *Nano Energy*, 2022, **100**, 107445.
- 48 C. Szczuka, R. A. Eichel and J. Granwehr, *RSC Adv.*, 2023, **13**, 14565.
- 49 C. H. Lee, S. Pahari, N. Sitapure, M. A. Barteau and J. S. Kwon, *ACS Catal.*, 2023, **13**, 8336.
- 50 Y. Luo, Y. Guan, G. Liu, Y. Wang, J. Li and L. Ricardez-Sandoval, *ACS Catal.*, 2024, **14**, 2696–2708.
- 51 J. Di, C. Chen, C. Zhu, R. Long, H. Chen, X. Cao, J. Xiong, Y. Weng, L. Song, S. Li, H. Li, Y. Xiong and Z. Liu, *Adv. Energy Mater.*, 2021, **11**, 2102389.