



Cite this: *CrystEngComm*, 2020, 22, 6239

## Optimization of the overall water-splitting performance of N, S co-doped carbon-supported NiCoMnS<sub>x-10</sub> at high current densities by the introduction of sulfur defects and oxygen vacancies†

Runzhi Zhang,<sup>a</sup> Zebin Yu,<sup>id</sup> \*<sup>ab</sup> Ronghua Jiang,<sup>c</sup> Jun Huang,<sup>de</sup> Yanping Hou,<sup>id</sup> <sup>a</sup> Qiuyue Zhou,<sup>a</sup> Shiyu Zhu,<sup>a</sup> Xiaocan Huang,<sup>a</sup> Feng Zheng<sup>a</sup> and Zhao Luo<sup>a</sup>

Designing an electrocatalyst with excellent performance for both the hydrogen evolution reaction and oxygen evolution reaction in overall water splitting is essential to promote the development of electrolyzed hydrogen production. Defect engineering is a promising method to improve the catalytic performance of target materials. In this study, we used a metal-organic framework as a precursor to establish oxygen-vacancy-rich metal oxide groups supported by a defect-rich carbon framework *via* calcination. Further, thermal ion exchange was performed to introduce sulfur ions to generate NiCoMnS<sub>x-10</sub> with both oxygen vacancies and sulfur defects. Due to the synergistic effect between oxygen vacancies and sulfur defects as well as the good morphology, NiCoMnS<sub>x-10</sub> exhibited good catalytic performance at high current densities. The NiCoMnS<sub>x-10</sub> cell could achieve a current density of 10 mA cm<sup>-2</sup> at a cell voltage of 1.506 V and a current density of 100 mA cm<sup>-2</sup> at an overpotential of only 1.94 V, which exceeds that of most materials reported to date. Due to the supporting effect of N, S co-doped carbon, the NiCoMnS<sub>x-10</sub> cell maintained stable performance during a 100 h operation at high current. This work provides an innovative method for the preparation of highly efficient electrocatalysts for overall water splitting.

Received 25th July 2020,  
Accepted 20th August 2020

DOI: 10.1039/d0ce01075h

[rsc.li/crystengcomm](http://rsc.li/crystengcomm)

## Introduction

Continuous attention on global energy and environmental issues has stimulated comprehensive research on efficient, natural, environment friendly, and sustainable alternate energy systems.<sup>1,2</sup> It has been found that the electrocatalytic overall water splitting to H<sub>2</sub> and O<sub>2</sub> through the hydrogen evolution reaction (HER) and oxygen evolution reaction (OER) is a promising technology to expand the production of clean and renewable energy.<sup>3-5</sup> This technology requires highly efficient HER and OER catalysts to overcome the high

overpotential generated by the two half reactions. Pt and RuO<sub>x</sub> are used as traditional benchmark electrocatalysts for the HER and OER, respectively. However, their scarcity and high cost hinder their widespread application. Based on the current situation, the search for an efficient, stable, and noble metal-free bifunctional electrocatalyst is booming in the field of electrocatalytic overall water splitting.<sup>6-8</sup>

In recent years, transition metal chalcogenide materials have been widely studied for overall water splitting due to their remarkable electroactivity, lower metal-H adsorption bond energy, and higher hydrogen dissociation properties.<sup>9,10</sup> However, structural problems, including single active sites and excessive order, are great challenges in the practical application of single metal sulfides as they significantly limit the catalytic performance. To solve this problem, researchers have tried to construct polycrystalline hybrid sulfides to modify the interface and surface defects of sulfides and adjust their electronic structure.<sup>11,12</sup> The introduction of a disordered structure into a catalyst may be a prospective way to improve the intrinsic catalytic performance. Oxygen vacancies can cause the redistribution of electrons on the catalyst surface during the catalytic process; this further improves the catalytic performance of the catalysts. Moreover, oxygen

<sup>a</sup> School of Resources, Environment and Materials, Guangxi University, Nanning 530004, P. R. China. E-mail: xxzx7514@hotmail.com, yuzebin@gxu.edu.cn; Tel: + 8613877108420

<sup>b</sup> Guangxi Key Laboratory of Clean Pulp & Papermaking and Pollution Control, Nanning 530004, P. R. China

<sup>c</sup> School of Chemical and Environmental Engineering, Shaoguan University, Shaoguan 512005, P. R. China

<sup>d</sup> College of Civil Engineering and Architecture, Guangxi University, Nanning 530004, P. R. China

<sup>e</sup> Hualan Design & Consulting Group, Nanning 530004, P. R. China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d0ce01075h

vacancies can reduce the adsorption barrier of the OH<sup>-</sup> anions generated during the catalytic reaction and can significantly improve the reactivity of the catalytic active sites;<sup>13,14</sup> accordingly, the OER activity of the catalyst is substantially improved rather than the HER activity. However, sulfur defects, which are common in transition metal chalcogenide materials, have a significant impact on the HER catalytic activity as they expose other active edges.<sup>15,16</sup> Herein, we proposed a hypothesis that by simultaneously introducing oxygen vacancies and sulfur defects into a material, the hydrogen and oxygen evolution activities of the material can be excellently adjusted. Studies have shown that the oxide lattice breaks into a disordered distribution after the electronegative sulfur atom is incorporated into the material to produce more defect sites and enhance the active of low coordination oxygen.<sup>17,18</sup> Therefore, we can choose a multi-metal hybrid oxide as a precursor for thermal ion exchange to introduce sulfur atoms instead of oxygen atoms for the preparation of multi-metal hybrid sulfides with high-density oxygen vacancies and sulfur defects.

In this study, we introduced a metal-organic framework (MOF) material with a specific structure and used its organic part to construct a well-structured carbon skeleton as a support for active materials by carbonization. Furthermore, its metal oxide groups were used to prepare oxygen-vacancy-containing metal oxide precursors. Then, along with the introduction of a sulfur source, thermal ion exchange was performed at high temperatures to prepare a polymetallic hybrid sulfide anchored by a N, S co-doped carbon skeleton. The obtained catalytic material not only retained the original structure of the MOF with N, S co-doped carbon skeleton and high-speed electron transport capability, but also had a high concentration of oxygen vacancies and sulfur defects that would synergistically promote the overall water-splitting reaction. Results shows good catalytic effect of this material, and it remained stable during operation at high current densities for a long time. Our study provides an innovative method for the preparation of highly efficient electrocatalysts.

## Experimental

### Materials

Cobalt acetate tetrahydrate (C<sub>4</sub>H<sub>6</sub>CoO<sub>4</sub>·4H<sub>2</sub>O), manganese acetate tetrahydrate (C<sub>4</sub>H<sub>6</sub>MnO<sub>4</sub>·4H<sub>2</sub>O), urea, ammonium fluoride (NH<sub>4</sub>F), thioacetamide (TAA), 2-aminoterephthalic acid, and *N,N*-dimethylformamide (DMF) were supplied by Lantian Co., Ltd. (Nanning, China). Nickel foam (thickness: 1.7 mm, pores per linear inch: 120 ppi) was purchased from Suzhou Jialongde Foam Metals Co., Ltd. (Suzhou, China). All reagents were of analytical grade and directly used without further purification.

### Synthesis

**Pretreatment of NF.** NF (2.0 cm × 3.0 cm × 0.17 cm) was ultrasonicated for 10 minutes with 1 M H<sub>2</sub>SO<sub>4</sub>, ethanol, and deionized water.

**Synthesis of NiCoMn(OH)<sub>x</sub>.** C<sub>4</sub>H<sub>6</sub>MnO<sub>4</sub>·4H<sub>2</sub>O and 0.005 M C<sub>4</sub>H<sub>6</sub>CoO<sub>4</sub>·4H<sub>2</sub>O were dissolved in 20 ml deionized water followed by stirring for 20 minutes. After the solution was completely mixed, 100 mg NH<sub>4</sub>F and 200 mg urea were added to the abovementioned mixture followed by stirring for another 20 minutes. The resulting mixture was transferred to a 50 ml Teflon-lined autoclave, and the treated NF was added followed by reaction at 120 °C for 12 h. The resulting product was labeled NCM(OH)<sub>x</sub>.

**Synthesis of NiCoMn(BDC)<sub>x</sub>.** Typically, 300 mg 2-aminoterephthalic acid was dissolved in 20 ml DMF followed by stirring for 20 minutes. Then, the abovementioned solution was transferred to a 50 ml Teflon-lined autoclave, and NCM(OH)<sub>x</sub>/NF was added followed by reaction at 160 °C for 5, 10, 15, and 20 h. The resulting products were labeled NCM(BDC)<sub>x-5</sub>, NCM(BDC)<sub>x-10</sub>, NCM(BDC)<sub>x-15</sub>, and NCM(BDC)<sub>x-20</sub>.

**Synthesis of NiCoMnO<sub>x</sub>.** The NCM(BDC)<sub>x</sub>/NF electrodes prepared at different reaction times in the previous step were put in a quartz boat, and then, the quartz boat was placed in a tube furnace. Under a protective nitrogen atmosphere, the temperature was increased to 400 °C at the heating rate of 5 °C min<sup>-1</sup> and then maintained for 3 hours. After the reaction was completed, the reaction mixture was allowed to cool to room temperature and then taken out. The resulting products were labeled NCMO<sub>x-5</sub>, NCMO<sub>x-10</sub>, NCMO<sub>x-15</sub>, and NCMO<sub>x-20</sub>.

**Synthesis of NiCoMnS<sub>x</sub>.** Herein, 300 mg TAA was dissolved in 20 ml ethanol followed by stirring for 15 minutes, and the resulting solution was transferred to a 50 ml Teflon-lined autoclave; the NCMO<sub>x</sub> grown on nickel foam in the previous step was also added to the autoclave followed by reaction at 160 °C for 3 h. The resulting products were labeled NCMS<sub>x-5</sub>, NCMS<sub>x-10</sub>, NCMS<sub>x-15</sub>, and NCMS<sub>x-20</sub>.

### Physicochemical characterizations

The synthesized materials were characterized by various techniques. The crystal structures of the materials were characterized by X-ray diffraction (XRD; Rigaku D/MAX-2500V, Rigaku Corporation) in the 2θ range of 5–90° at the scanning rate of 10° min<sup>-1</sup>. The degree of graphitization of the prepared electrodes was determined using a Raman spectrometer (Renishaw inVia Reflex) at room temperature with a 532 nm laser and a source spectral range of 1000–2000 cm<sup>-1</sup>. The samples were subjected to Fourier transform infrared (FTIR) spectroscopy using a Fourier transform infrared spectrometer (Nicolet iS 50, Somerfly, USA) with KBr as a diluent. X-ray photoelectron spectroscopy (XPS) was performed using an X-ray photoelectron spectrometer (ESCALAB 250XI+, Thermo Fisher Scientific) equipped with an Al (single) X-ray source and calibrated against a variable carbon signal (binding energy = 284.8 eV). The element content of the materials was analyzed using an ICP-AES inductively coupled plasma emission spectrometer (model ICPS-7510, Shimadzu).

Corporation). Scanning electron microscopy (SEM) images were acquired using an SU8020 (Hitachi High-tech) instrument at an accelerating voltage of 10 kV. Transmission electron microscopy (TEM) images were obtained by a FEI TECNAI G2 F30 instrument. The hydrophilicity of the materials was tested using a contact-angle measuring instrument (model DSA100E, German KYUSS company). Using the OmniFluo-960 fluorescence spectrometer, photoluminescence (PL) spectra were obtained at the excitation wavelengths of 285 nm and 532 nm.

### Electrochemical characterization

An electrochemical workstation (CHI 660E, China) with a typical three-electrode system was used for all the electrochemical tests. Herein, 1 M KOH was used as an electrolyte for all the electrochemical tests. The prepared catalyst materials were used as the working electrode, a graphite rod electrode was used as the counter electrode, and saturated Hg|HgO|OH<sup>-</sup> was employed as the reference electrode to examine the performance of HER and OER. The prepared electrode materials were simultaneously used as an anode and a cathode, and the performance of overall water splitting was obtained using a two-electrode system. Before the electrochemical tests, the electrolyte was purged with N<sub>2</sub> for 30 min to remove O<sub>2</sub>. For parallel comparison with literature values, the potentials were measured vs. Hg|HgO|OH<sup>-</sup> and converted to the reversible hydrogen electrode (RHE) scale according to the Nernst equation:

$$E(\text{RHE}) = E(\text{vs. Hg|HgO|OH}^-) + 0.059 \text{ pH} + 0.098 \text{ V}$$

For the HER performance, a CV negative scan was performed in the range from -2 to 0 V relative to Hg|HgO|OH<sup>-</sup> at the scan rate of 2 mV s<sup>-1</sup>, and its polarization curve was obtained. The durability was tested at the current density of 100 mA cm<sup>-2</sup> for 100 h. For the OER performance, a CV negative scan was performed in the range from 0 to 1.2 V relative to Hg|HgO|OH<sup>-</sup> at the scan rate of 2 mV s<sup>-1</sup>, and its polarization curve was acquired. The durability was tested at the current density of 100 mA cm<sup>-2</sup> for 100 h. Electrochemical impedance spectroscopy (EIS) was conducted in the frequency range of 100 kHz–0.01 Hz with an AC potential amplitude of 5 mV s<sup>-1</sup>. The measured impedance data were fitted with an equivalent circuit to obtain the series and charge transfer resistances (two-time-constant parallel (2TP) circuit model using Zsimpwin). All the CV tests were performed with iR compensation without stirring. However, no iR compensation was performed during the chronopotentiometry test.

## Results and discussion

### Physical properties

As shown in Scheme 1, 2-aminoterephthalic acid acted as an organic ligand, and nickel foam acted as a nickel source;



**Scheme 1** Using NiCoMn(BDC)<sub>x</sub> as a precursor, an anion exchange method was used to synthesize highly disordered NCMs<sub>x</sub> compounds.

cobalt and manganese salts were added to provide cobalt and manganese for the synthesis of NCM(BDC)<sub>x</sub>. Then, NCM(BDC)<sub>x</sub> was carbonized to obtain a well-structured N-doped carbon skeleton-supported NCMO<sub>x</sub> with oxygen vacancies. After this, the sulfur source was introduced for the thermal ion-exchange reaction, and N, S co-doped carbon skeleton-anchored NCMs<sub>x</sub> rich in oxygen vacancies and sulfur defects was obtained.

As shown in Fig. 1 and S1,<sup>†</sup> the morphologies of the synthesized materials were characterized by a scanning electron microscope (SEM). It can be observed from Fig. S1a–j<sup>†</sup> that when the reaction time was 5 h, the resulting material NCM(BDC)<sub>x-5</sub> retained the size of NCM(OH)<sub>x</sub> and showed agglomeration. With an increase in the reaction time, dispersed flower-like NCM(BDC)<sub>x-10</sub> was obtained. With a further increase in the reaction time, the petals continued to thicken, and NCM(BDC)<sub>x-15</sub> and NCM(BDC)<sub>x-20</sub> were achieved. Fig. 1a–d show the morphology of the pyrolysis products NCMO<sub>x</sub>; it can be observed that the pyrolysis products maintained the basic morphology of the original MOF; however, the petals became thinner. Among them, NCMO<sub>x-10</sub> exhibited well-connected three-dimensional flower-like sheets, which are conducive for a full contact between the active sites and the electrolyte and the conduction of electrons inside the material.

Fig. 1e–h show the morphology of the product obtained after vulcanization. Many thin, transparent, and small-sized sheets were noticed on the petals after vulcanization. NCMs<sub>x-5</sub> still showed an aggregated form (Fig. 1e), which was not conducive for the participation of deep active sites in the reaction. For NCMs<sub>x-15</sub> and NCMs<sub>x-20</sub> (Fig. 1g and h), as the petals of their precursors were too thick, only a few thin slices could be generated on the surface of these petals, and more sites were wrapped in them. The difference is that under the advantages of the precursor's just dispersion and proper thickness, NCMs<sub>x-10</sub> (Fig. 1f) shows a uniform state of small sheets intertwined after vulcanization. This morphology significantly increases the contact area between the material and the electrolyte, leading to the participation of more active sites in the reaction. In addition, under the combined effect of the high winding degree of the sheet



Fig. 1 SEM images of (a)  $\text{NCMO}_{x-5}$ ; (b)  $\text{NCMO}_{x-10}$ ; (c)  $\text{NCMO}_{x-15}$ ; (d)  $\text{NCMO}_{x-20}$ ; (e)  $\text{NCMS}_{x-5}$ ; (f)  $\text{NCMS}_{x-10}$ ; (g)  $\text{NCMS}_{x-15}$ ; and (h)  $\text{NCMS}_{x-20}$ .

structure and the carbon skeleton, the electron transfer within the material will be more convenient and fast.

In order to characterize the synthesis of the materials, XRD tests were performed on the materials, and the results are shown in Fig. S2a† and 2a–b. Fig. S2a† shows that the diffraction peaks in the XRD pattern of  $\text{NCM}(\text{BDC})_x$  basically correspond to  $\text{Ni}(\text{BDC})$ ,  $\text{Co}(\text{BDC})$ , and  $\text{Mn}(\text{BDC})$ . However, due to the interaction of different metal ions, a small shift was observed in some peaks of the polymetallic MOF as compared to the case of the monometallic MOF, which further verifies that the MOF synthesized herein is

polymetallic rather than a simple mixture of the three monometallic MOFs. As can be noticed in Fig. 2a and b, the characteristic diffraction peaks attributed to the MOF were retained in the patterns of both the oxide and sulfide; this indicates that even after pyrolysis and vulcanization, the characteristics of  $\text{NCM}(\text{BDC})_x$  were retained. In addition, the products achieved after pyrolysis, as shown in Fig. 2a, were a mixture of  $\text{NiO}$ ,  $\text{CoO}$ , and  $\text{Mn}_3\text{O}_4$ ; this proves the successful synthesis of oxide precursors. Similarly, as shown in Fig. 2b, after the thermal ion-exchange reaction, the sulfur atoms successfully replaced the oxygen atoms. The products obtained were a mixture of  $\text{Ni}_3\text{S}_2$ ,  $\text{Co}_3\text{S}_4$ , and  $\text{MnS}$ , which further proved the successful synthesis of  $\text{NCMS}_x$ .

In order to confirm the synthesis of MOFs and to characterize the functional groups in the precursor materials, FTIR was performed on  $\text{NCM}(\text{BDC})_x$ , and the FTIR spectra are shown in Fig. 2c. The peak observed at  $1380\text{ cm}^{-1}$  corresponds to the symmetric tensile vibration of the coordinated carboxylate group, indicating the successful coordination of  $\text{Co}^{2+}$  ions with BDC ligands, proving the successful synthesis of  $\text{Co}(\text{BDC})$ .<sup>19,20</sup> Furthermore, a peak corresponding to  $\text{Ni}(\text{BDC})$  was observed at  $508\text{ cm}^{-1}$ .<sup>21</sup> In addition, the spectrum displayed a peak at  $748\text{ cm}^{-1}$ , which is attributed to  $\text{Mn}(\text{BDC})$ .<sup>22</sup> The peaks related to the functional groups of organic ligands were also obtained in the spectra, in which the two bands at  $1032$  and  $808\text{ cm}^{-1}$  are attributed to the C–H tensile band.<sup>23</sup> Moreover, two obvious peaks were found in the range of  $1410$ – $1260\text{ cm}^{-1}$ , indicating the presence of –OH. The band at  $1450 \pm 20\text{ cm}^{-1}$  is a sign of C=C tensile vibration in the presence of an aromatic carbon network. The peak of the combination of N–H in-plane bending and C–N stretching was found at  $1548\text{ cm}^{-1}$ , demonstrating the retention of amino groups in the ligand. The analysis of the FTIR spectra further proves the successful synthesis of the MOF precursors.

The concentration of surface defects has a non-negligible effect on the performance of the material. In order to characterize the defects of the materials and prove the high disorder of the materials, Raman, PL, and EPR spectroscopy



Fig. 2 (a) XRD patterns of  $\text{NCMO}_x$ ; (b) XRD patterns of  $\text{NCMS}_x$ ; (c) FTIR spectra of  $\text{NCM}(\text{BDC})_x$ ; (d) Raman spectra of  $\text{NCMO}_x$  and  $\text{NCMS}_x$ ; (e) EPR spectra of  $\text{NCMO}_{x-10}$  and  $\text{NCMS}_{x-10}$ ; and (f) PL spectra of  $\text{NCMO}_x$  and  $\text{NCMS}_x$ .

tests were performed on the synthesized  $\text{NCMO}_x$  and  $\text{NCMS}_x$ . It can be noticed from the Raman spectrum shown in Fig. 2d that a defect-rich carbon skeleton with  $I_D:I_G > 1$  was successfully prepared after calcination. Among them, the carbon defect degree of  $\text{NCMO}_{x-10}$  was greater than that of the other three oxides. After vulcanization, due to the doping effect of sulfur atoms, the defect degree of the carbon skeleton was further increased; this implies the successful synthesis of N, S co-doped carbon. It can also be observed that the defect degree of  $\text{NCMS}_{x-10}$  is slightly larger than those of the other materials.

In addition, as shown in Fig. 2e, the EPR curves prove that there are oxygen vacancies in  $\text{NCMO}_{x-10}$ , whereas there may be both oxygen vacancies and sulfur defects in  $\text{NCMS}_{x-10}$ .<sup>24–27</sup> It can be verified that the synthesized  $\text{NCMO}_{x-10}$  and  $\text{NCMS}_{x-10}$  are rich in defects and show a high disorder. After this, the specific defects of the materials were characterized by PL spectroscopy. As can be observed from the small graph shown in Fig. 2f, at an excitation wavelength of 532 nm, the spectrum of  $\text{NCMS}_x$  showed a peak at 680 nm that was attributed to the S defects.<sup>28–30</sup> However, the spectrum of  $\text{NCMO}_x$  does not have this peak, indicating that the  $\text{NCMS}_x$  compounds containing sulfur defects were successfully prepared. However, at the excitation wavelength of 285 nm, the spectra of all the  $\text{NCMO}_x$  and  $\text{NCMS}_x$  compounds showed a peak at 410 nm corresponding to oxygen vacancies.<sup>31,32</sup> Interestingly, the peak intensity of the vulcanized product was higher than that of the oxide precursor; this shows that the concentration of the oxygen vacancies increases after vulcanization. This further verifies that after the introduction of negatively charged sulfur, the oxide lattice is decomposed into a disordered arrangement, thereby generating more defect sites and enhancing the active of low coordination oxygen. These characteristics of the materials rich in oxygen vacancies and sulfur defects are very beneficial for achieving efficient overall water splitting.

XPS was performed to explore the elemental characteristics of the material, and the results are shown in Fig. 3. As shown in Fig. 3a, the peaks at 284.5, 285.1, and 288.3 eV correspond to the C–C, C=C, and C=O bonds.<sup>33,34</sup> Furthermore, the binding energy peaks at 284.1 and 285.5 eV can be assigned to C–S and C–N, respectively.<sup>33,35</sup> This proves the successful synthesis of the N-doped carbon skeleton in  $\text{NCMO}_{x-10}$  and the successful synthesis of N, S co-doped carbon in  $\text{NCMS}_{x-10}$ . The peaks corresponding to pyridinic N (398.3 eV), pyrrolic N (399.4 eV), and graphitic N (400.7 eV) were found in the high-resolution N 1s spectrum (Fig. 3b),<sup>35–37</sup> and the presence of the graphitic N peak further proves that N was doped into the carbon skeleton. We found that pyridinic N and pyrrolic N coexist in  $\text{NCMS}_{x-10}$ , whereas only pyridinic N exists in  $\text{NCMO}_{x-10}$ . The presence of pyrrolic N and pyridinic N proves that the material can exhibit improved electrocatalytic activity by interacting with  $\text{H}^+$  for the HER or bind to OER intermediates ( $\text{O}^*$ ,  $\text{OOH}^*$ , or  $\text{OH}^*$ ) under appropriate force.<sup>38,39</sup> Therefore, the performance of the material having both pyrrolic N and pyridinic N will be more excellent. Thus, it is inferred that the electrocatalytic

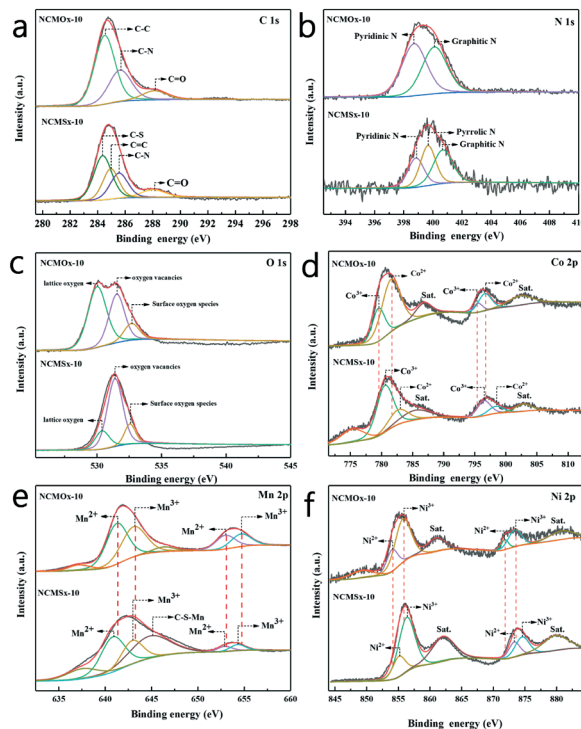


Fig. 3 (a–f) C 1s, N 1s, O 1s, Co 2p, Mn 2p, and Ni 2p spectra of  $\text{NCMO}_{x-10}$  and  $\text{NCMS}_{x-10}$ .

performance of  $\text{NCMS}_{x-10}$  will be better than that of  $\text{NCMO}_{x-10}$ . In addition, there are peaks at 531.4 eV, 530.2 eV, and 532.2 eV, attributed to lattice oxygen, oxygen vacancies, and surface oxygen adsorption, in the O 1s spectrum (Fig. 3c) of the materials.<sup>40,41</sup> The analysis of the O 1s spectrum shows that there are oxygen vacancies in both  $\text{NCMO}_{x-10}$  and  $\text{NCMS}_{x-10}$ . From the peak areas, it can be analyzed that the concentration of oxygen vacancies in  $\text{NCMS}_{x-10}$  is even higher than that in  $\text{NCMO}_{x-10}$ , and this conclusion agrees well with the PL results.

In the Co 2p spectrum (Fig. 3d), the peaks at 779.5 and 795.1 eV are attributed to  $\text{Co}^{3+}$  ( $2p_{3/2}$ ) and  $\text{Co}^{3+}$  ( $2p_{1/2}$ ), respectively, and the two peaks at 781.3 and 795.9 eV correspond to  $\text{Co}^{2+}$  ( $2p_{3/2}$ ) and  $\text{Co}^{2+}$  ( $2p_{1/2}$ ). The two peaks obtained at 787.1 and 802.6 eV are satellite peaks.<sup>31,32,42</sup> As shown in Fig. 3e, the two peaks at 641.0 and 652.5 eV can be assigned to  $\text{Mn}^{2+}$ , and the other two peaks at 642.2 and 653.7 eV can be attributed to  $\text{Mn}^{3+}$ .<sup>41,43</sup> In addition, the peak at 644.3 eV can be assigned to C–S–Mn.<sup>44,45</sup> The Ni 2p spectrum shown in Fig. 3f was analyzed, and the fitted peaks at 854.0 and 871.80 eV were attributed to the  $\text{Ni}^{2+}$  ions, whereas the fitted peaks at 855.70 and 873.40 eV were assigned to the  $\text{Ni}^{3+}$  ions.<sup>46,47</sup> Via a comparative analysis of the XPS spectra of  $\text{NCMO}_{x-10}$  and  $\text{NCMS}_{x-10}$ , we found a regular phenomenon. When the sulfur atoms replace the oxygen atoms, the XPS peaks of different metals have different degrees of displacement; this shows that with the addition of sulfur atoms, a strong charge transfer occurs inside the material.

The morphology and lattice conditions of the materials were observed using a projection electron microscope, as shown in Fig. 4. As shown in Fig. 4a, NCMS<sub>x</sub> exhibits a cross-linked film shape, which can provide more channels for electron transfer. In the HRTEM image (Fig. 4b), lattice fringes belonging to the MnS (201) crystal plane and Ni<sub>3</sub>S<sub>2</sub> (210) crystal plane can be observed, and there are some parts without lattice spacing, which is due to the presence of N, S co-doped carbon. Moreover, the lattice fringes in Fig. 4c can be assigned to Co<sub>3</sub>S<sub>4</sub>(311), Ni<sub>3</sub>S<sub>2</sub>(200), and MnS(110). It can be observed from the HRTEM images (Fig. 4b and c) that the lattice fringes of NCMS<sub>x-10</sub> are highly disordered, and this high disorder is also closely related to the defect-rich features of NCMS<sub>x-10</sub>. In addition, the morphology of the other NCMS<sub>x</sub> compounds was examined. It can be noticed that the NCMS<sub>x-5</sub> (Fig. 4d) film is relatively dispersed and flat, and the electron transfer is limited by the number of channels. Moreover, NCMS<sub>x-15</sub> and NCMS<sub>x-20</sub> (Fig. 4e and f) exhibit aggregation phenomena, which is not conducive for the contact between the reaction site and the electrolyte, respectively. On the other hand, the morphology of NCMS<sub>x-10</sub> is helpful for the electrocatalytic reaction.

In addition, the atomic ratios of Co and Mn in NCM(BDC)<sub>x</sub> prepared at different reaction times were analyzed by the ICP-OES analysis (the proportion of the Ni element could not be accurately estimated due to the influence of the nickel substrate), and the results are shown in Table S1.† The atomic ratios of Co and Mn in NCM(BDC)<sub>x-5</sub>, NCM(BDC)<sub>x-10</sub>, NCM(BDC)<sub>x-15</sub>, and NCM(BDC)<sub>x-20</sub> are 1:0.88, 1:0.99, 1:1.01, and 1:0.82; it can be observed that the atomic ratios of Co and Mn in different

materials are close to 1. In addition, the hydrophilicity of different NCMS<sub>x</sub> was investigated. As shown in Fig. S3,† the contact angle of NCMS<sub>x-10</sub> is the smallest and its hydrophilicity is the best, which is most conducive for the full contact of the material with the electrolyte. This feature is also one of the reasons for the best catalytic performance of NCMS<sub>x-10</sub>.

## HER performance

Using a typical three-electrode system in 1.0 M KOH with the obtained materials as the working electrodes, the electrocatalytic performance of these materials for the HER was evaluated at a scan rate of 2 mV s<sup>-1</sup>. In order to verify the applicability of these materials in the industry, we compared the performances of the materials at high current densities. It can be observed from Fig. 5a and Table S4† that when the current density was 10 mA cm<sup>-2</sup>, the overpotential of NCMS<sub>x-10</sub> was only -105 mV, which was far lower than those of other comparative materials. Similarly, when the current density reached the industrial application standard of 100 mA cm<sup>-2</sup>, the required overpotential of NCMS<sub>x-10</sub> (-330 mV) was substantially smaller than those of NCMO<sub>x-5</sub> (-429 mV), NCMO<sub>x-10</sub> (-401 mV), NCMO<sub>x-15</sub> (-423 mV), NCMO<sub>x-20</sub> (-448 mV), NCMS<sub>x-5</sub> (-352 mV), NCMS<sub>x-15</sub> (-365 mV), and NCMS<sub>x-20</sub> (-372 mV). This performance gap is mainly because the well-crosslinked film morphology of the material provides a fast electron channel, and the rich sulfur defects are also beneficial for the HER.

Fig. 5b shows the EIS curves of the materials and the corresponding fitted circuit diagrams, and the EIS-related data of the materials is provided in Table S2.† From these data, we can observe that the R<sub>ct</sub> (charge transfer resistance) of NCMS<sub>x-10</sub> (37.37 Ω) is significantly smaller than those of NCMO<sub>x-5</sub> (168.10 Ω), NCMO<sub>x-10</sub> (129.80 Ω), NCMO<sub>x-15</sub>



Fig. 4 (a) TEM image of NCMS<sub>x-10</sub>; (b and c) HRTEM images of NCMS<sub>x-10</sub>; (d) TEM image of NCMS<sub>x-5</sub>; (e) TEM image of NCMS<sub>x-15</sub>; and (f) TEM image of NCMS<sub>x-20</sub>.



Fig. 5 (a) HER polarization curves (iR-corrected) obtained at a scan rate of 2 mV s<sup>-1</sup>; (b) HER electrical impedance maps; (c) the Tafel slopes of the materials; and (d) results of the 100 h chronopotentiometry test of NCMS<sub>x</sub> under HER.

(195.80  $\Omega$ ),  $\text{NCMO}_{x-20}$  (222.1  $\Omega$ ),  $\text{NCMS}_{x-5}$  (38.07  $\Omega$ ),  $\text{NCMS}_{x-15}$  (99.24  $\Omega$ ), and  $\text{NCMS}_{x-20}$  (129.20  $\Omega$ ). This is due to the presence of the N, S co-doped carbon framework and the well-crosslinked morphology of the material. Fig. 5c presents the Tafel slopes of these electrodes. Compared with  $\text{NCMO}_{x-5}$  (136  $\text{mV dec}^{-1}$ ),  $\text{NCMO}_{x-10}$  (130  $\text{mV dec}^{-1}$ ),  $\text{NCMO}_{x-15}$  (142  $\text{mV dec}^{-1}$ ),  $\text{NCMO}_{x-20}$  (163  $\text{mV dec}^{-1}$ ),  $\text{NCMS}_{x-5}$  (121  $\text{mV dec}^{-1}$ ),  $\text{NCMS}_{x-15}$  (123  $\text{mV dec}^{-1}$ ), and  $\text{NCMS}_{x-20}$  (128  $\text{mV dec}^{-1}$ ),  $\text{NCMS}_{x-10}$  has the smallest Tafel slope (116  $\text{mV dec}^{-1}$ ). This indicates that the rate of apparent hydrogen formation rapidly increases with an increase in the applied potential. In order to explore the stability of the material at high current densities,  $\text{NCMS}_{x-10}$  was subjected to chronopotentiometry for 100 hours under the HER reaction. Fig. 5d shows that the change in the overpotential was negligible after 100 h, indicating that  $\text{NCMS}_{x-10}$  has good stability.

### OER performance

Similarly, the OER performance of the catalyst was evaluated at a scan rate of 2  $\text{mV s}^{-1}$  in a 1.0 M KOH solution. Consistent with the results of HER,  $\text{NCMS}_{x-10}$  exhibited better performance than other materials due to the synergetic effect of good morphology, more abundant defects, and N, S co-doped carbon. As shown in Fig. 6a and Table S4,†  $\text{NCMS}_{x-10}$  requires an overpotential of only 226 mV to achieve a current density of 10  $\text{mA cm}^{-2}$ . Moreover, the current density could reach 100  $\text{mA cm}^{-2}$  at a voltage of 417 mV, which was better than those of  $\text{NCMO}_{x-5}$  (564 mV),  $\text{NCMO}_{x-10}$  (557 mV),  $\text{NCMO}_{x-15}$  (568 mV),  $\text{NCMO}_{x-20}$  (579 mV),  $\text{NCMS}_{x-5}$  (440 mV),  $\text{NCMS}_{x-15}$  (453 mV), and  $\text{NCMS}_{x-20}$  (472 mV).

Fig. 6b shows the EIS curves of the materials and the corresponding fitted circuit diagrams, and the EIS-related data of the materials is provided in Table S3.† It can be noticed from the comparison that the  $R_{ct}$  (74.73  $\Omega$ ) of

$\text{NCMS}_{x-10}$  is smaller than those of  $\text{NCMO}_{x-5}$  (179.11  $\Omega$ ),  $\text{NCMO}_{x-10}$  (142.70  $\Omega$ ),  $\text{NCMO}_{x-15}$  (199.92  $\Omega$ ),  $\text{NCMO}_{x-20}$  (243.84  $\Omega$ ),  $\text{NCMS}_{x-5}$  (123.21  $\Omega$ ),  $\text{NCMS}_{x-15}$  (124.22  $\Omega$ ), and  $\text{NCMS}_{x-20}$  (127.80  $\Omega$ ); this shows that  $\text{NCMS}_{x-10}$  has ultra-fast charge transfer capability and can lead to a higher reaction rate. It can be noticed in Fig. 6c that  $\text{NCMS}_{x-10}$  has a Tafel slope of 107  $\text{mV dec}^{-1}$ , which is lower than those of  $\text{NCMO}_{x-5}$  (160  $\text{mV dec}^{-1}$ ),  $\text{NCMO}_{x-10}$  (139  $\text{mV dec}^{-1}$ ),  $\text{NCMO}_{x-15}$  (151  $\text{mV dec}^{-1}$ ),  $\text{NCMO}_{x-20}$  (165  $\text{mV dec}^{-1}$ ),  $\text{NCMS}_{x-5}$  (115  $\text{mV dec}^{-1}$ ),  $\text{NCMS}_{x-15}$  (118  $\text{mV dec}^{-1}$ ), and  $\text{NCMS}_{x-20}$  (128  $\text{mV dec}^{-1}$ ). This indicates that  $\text{NCMS}_{x-10}$  is kinetically advantageous for the OER. In order to explore the stability of  $\text{NCMS}_{x-10}$  at high current densities in the OER, a 100 h chronopotentiometry test was performed at a current density of 100  $\text{mA cm}^{-2}$ , and the overpotential curve showed a slight change (Fig. 6d), confirming the stability of  $\text{NCMS}_{x-10}$  in the OER.

### Overall water-splitting performance

By conducting the HER and OER using the proposed materials, we determined the feasibility of using  $\text{NCMS}_{x-10}$  as a bifunctional catalyst. In order to explore its overall water-splitting performance, we simultaneously used  $\text{NCMS}_{x-10}$  as a positive electrode and negative electrode in an alkaline electrolysis cell at a scan rate of 2  $\text{mV s}^{-1}$  and conducted the overall water-splitting reaction. Fig. 7a and Table S4† show that the  $\text{NCMS}_{x-10}$  cell can achieve the current density of 10  $\text{mA cm}^{-2}$  at the cell voltage of 1.506 V, obtaining a current density of 100  $\text{mA cm}^{-2}$  at an overpotential of only 1.94 V. It can also be observed in Fig. 7a that when the current density is 100  $\text{mA cm}^{-2}$ , the  $\text{NCMS}_{x-10}$  cell exhibits the smallest voltage value when compared with the  $\text{NCMO}_{x-5}$  cell (2.24 V),  $\text{NCMO}_{x-10}$  cell (2.23 V),  $\text{NCMO}_{x-15}$  cell (2.28 V),  $\text{NCMO}_{x-20}$  cell (2.32 V),  $\text{NCMS}_{x-5}$  cell (2.10 V),  $\text{NCMS}_{x-15}$  cell (2.05 V), and

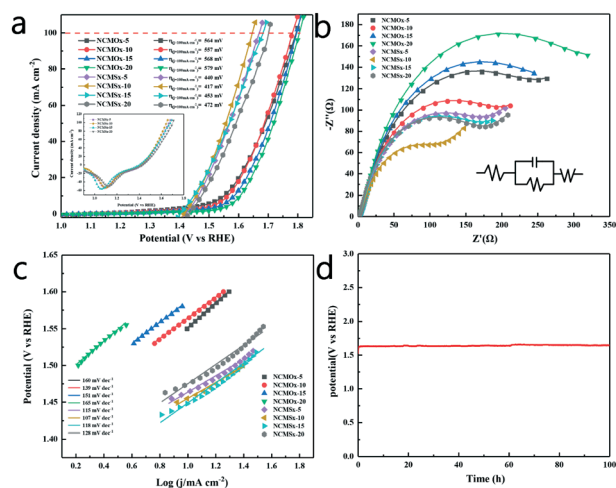


Fig. 6 (a) OER polarization curves (iR-corrected) at a scan rate of 2  $\text{mV s}^{-1}$ ; (b) OER electrical impedance maps; (c) the Tafel slopes of the materials; and (d) results of the 100 h chronopotentiometry test of  $\text{NCMS}_{x-10}$  under the OER.

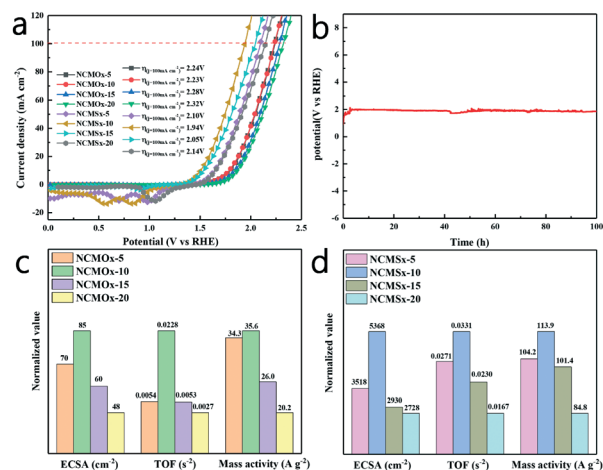


Fig. 7 (a) Polarization curves (iR-corrected) in the two-electrode configuration; (b) chronopotentiometry test of  $\text{NCMS}_{x-10}$  under overall water splitting; (c) comparison between the activities of different  $\text{NCMO}_x$  materials in 1.0 M KOH; and (d) comparison between the activities of different  $\text{NCMS}_x$  materials in 1.0 M KOH.

NCMS<sub>x-20</sub> cell (2.14 V). Upon further comparing NCMS<sub>x-10</sub> with the current noble-metal-free catalysts (Table S5†), it was found that NCMS<sub>x-10</sub> has the best overall water-splitting catalytic performance. Thus, NCMS<sub>x-10</sub> anchored by N, S co-doped carbon and rich in oxygen vacancies and sulfur defects exhibits excellent performance in catalyzing the overall water-splitting reaction. As shown in Fig. 7b, a 100 h chronopotentiometry test was performed at a current density of 100 mA cm<sup>-2</sup>, and the overpotential curve showed a slight change, confirming the stability of NCMS<sub>x-10</sub> in the overall water-splitting reaction.

In order to more comprehensively evaluate and compare the performances of these materials in overall water splitting, different electrochemical parameters were evaluated using different electrochemical parameter calculation methods (supporting materials). As shown in Fig. 7c and d, the mass activity, ECSA (electrochemically active surface area), and TOF (turn over frequency) of NCMO<sub>x</sub> and NCMS<sub>x</sub> were investigated to evaluate the properties of these materials. We calculated the double-layer capacitance ( $C_{dl}$ ) of these materials based on their CV curves (Fig. S4†) and then evaluated the ECSA of these materials to determine their intrinsic activity (Fig. S5†). As shown in Fig. 7c and d, the ECSA of NCMS<sub>x-10</sub> is the largest (5368 cm<sup>2</sup>). The ECSAs of other materials are as follows: NCMO<sub>x-5</sub> (70 cm<sup>2</sup>), NCMO<sub>x-10</sub> (85 cm<sup>2</sup>), NCMO<sub>x-15</sub> (60 cm<sup>2</sup>), NCMO<sub>x-20</sub> (48 cm<sup>2</sup>), NCMS<sub>x-5</sub> (3518 cm<sup>2</sup>), NCMS<sub>x-15</sub> (2930 cm<sup>2</sup>), and NCMS<sub>x-20</sub> (2728 cm<sup>2</sup>). Moreover, *via* the values of mass activity, the performances of the electrocatalysts can be determined. The values of mass activity are as follows: NCMS<sub>x-10</sub> (113.9 A g<sup>-1</sup>), NCMO<sub>x-5</sub> (34.3 A g<sup>-1</sup>), NCMO<sub>x-10</sub> (35.6 A g<sup>-1</sup>), NCMO<sub>x-15</sub> (26.0 A g<sup>-1</sup>), NCMO<sub>x-20</sub> (20.2 A g<sup>-1</sup>), NCMS<sub>x-5</sub> (104.2 A g<sup>-1</sup>), NCMS<sub>x-15</sub> (101.4 A g<sup>-1</sup>), and NCMS<sub>x-20</sub> (84.8 A g<sup>-1</sup>). The ECSA and mass activity results are consistent with those obtained *via* polarization curves. In addition, the TOF of NCMS<sub>x-10</sub> is also the largest, which reached 0.0331 s<sup>-1</sup>, whereas the TOFs of NCMO<sub>x-5</sub>, NCMO<sub>x-10</sub>, NCMO<sub>x-15</sub>, NCMO<sub>x-20</sub>, NCMS<sub>x-5</sub>, NCMS<sub>x-15</sub>, and NCMS<sub>x-20</sub> are 0.0054 s<sup>-1</sup>, 0.0228 s<sup>-1</sup>, 0.0053 s<sup>-1</sup>, 0.0027 s<sup>-1</sup>, 0.0271 s<sup>-1</sup>, 0.0230 s<sup>-1</sup>, and 0.0167 s<sup>-1</sup>, respectively. Based on these parameters, we can conclude that NCMS<sub>x-10</sub> has better performance than other materials in all aspects due to the synergistic effect of good morphology, abundant oxygen vacancies, and sulfur defects.

### Discussion of stability

In order to verify the stability and explore the change in the valence band of the material after different reaction processes to infer the possible reaction active sites, we performed XRD, PL, SEM, and XPS characterizations of the material after 100 hours of OER and HER chronopotentiometry test. It can be observed that there is no obvious change in the XRD pattern of the material (Fig. S6a†) after the reactions; this shows that neither the OER nor the HER affected the crystal structure of the material; this further illustrates the stability of the material. In addition, it can be

noticed in Fig. S6b and c† that the intensity of the PL peaks of sulfur defects and oxygen vacancies slightly increased after the reaction; this may be caused by the leaching of a small amount of sulfide ions and oxidation reactions during the test. However, this change is so tiny that it can even be ignored. This indicates that the content of oxygen vacancies and sulfur defects in the material is basically maintained before and after the reaction, which further illustrates the stability of the material.

The XPS spectrum (Fig. S7†) shows the peaks of the elements with relatively obvious changes. It can be observed that compared with those before the reaction, the valence state of the metal elements and the ratio of different valence states had no obvious changes after the HER, and no new substances were produced; however, there are different degrees of deviation. This shows that the material could still maintain a relatively stable state after 100 hours of high-current hydrogen evolution reaction. After the OER, although the valence state of the metal element did not significantly change, the valence state ratio of the ion changed when compared with that before the reaction. Furthermore, the peak of CoO was observed in the Co 2p spectrum, which indicates that during the OER, the surface of the material was partially oxidized, and metal oxides with strong oxygen evolution properties were generated. This change could promote the OER.

*Via* the analysis of the S 2p spectrum, it can be found that the noise level of the S 2p spectrum increased after the HER and OER; this indicates that the leaching of the S element occurred during these two half reactions, and the leaching of S during the OER was most obvious. The stability test results show that the OER performance (Fig. 6d) is very stable, indicating that the leaching of sulfur ions does not affect the progress of the OER. Although there is leaching of only a small amount of S ions during the HER (Fig. 5d), the stability of the HER performance still significantly fluctuated. This shows that the S ion has a significant effect on the HER performance, whereas the effect on the OER performance is negligible.

As shown in Fig. S8a,† NCMS<sub>x-10</sub> slightly aggregated after the HER; however, the basic morphology of NCMS<sub>x-10</sub> was retained. Moreover, the SEM image (Fig. S8b†) obtained after the OER showed that the flower-like structure of NCMS<sub>x-10</sub> was destroyed, the pore size of the material became larger, and the interlacing degree of the sheet structure reduced. By combining the analysis results of PL and XPS acquired after the reaction, it can be inferred that this phenomenon may be due to the leaching of the S element and the formation of an oxide film during the OER.

## Conclusions

In summary, herein, we used an MOF material as a precursor and performed calcination and thermal ion exchange to successfully prepare N, S co-doped carbon framework-anchored NCMS<sub>x-10</sub> with abundant oxygen vacancies and

sulfur defects. The oxygen vacancies and sulfur defects contributed to the improvement of the OER and HER performances, respectively. Due to the synergistic effect of oxygen vacancies and sulfur defects and morphology control, the material showed excellent performance. The NCMS<sub>x-10</sub> cell could achieve a current density of 100 mA cm<sup>-2</sup> at an overpotential of only 1.94 V. Moreover, at the high current density of 100 mA cm<sup>-2</sup>, this cell could operate stably for 100 h, indicating that NCMS<sub>x-10</sub> is an excellent electrocatalytic material. This study provides an available solution for further promoting the development of non-noble metal catalysts.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors gratefully acknowledge the support provided by the Guangxi Natural Science Foundation (No. 2017GXNSFBA198186, 2018GXNSFAA281290, and 2018GXNSFAA294062), National innovation program for College Students (202010593047), China Post-Doctoral Science Foundation Grant (No. 2018M633295), Young Teachers Innovation Cultivation Program (BRP180261) from the Guangxi Bossco Environmental Protection Technology Co., Ltd., and Open Fund of Guangxi Key Laboratory of Clean Pulp & Papermaking and Pollution Control (No. 2019KF19).

## References

- J. Yang, X. Wang, B. Li, L. Ma, L. Shi, Y. Xiong and H. Xu, *Adv. Funct. Mater.*, 2017, **27**, 1606497.
- F. Si, C. Tang, Q. Gao, F. Peng, S. Zhang, Y. Fang and S. Yang, *J. Mater. Chem. A*, 2020, **8**, 3083–3096.
- B. Ye, L. Huang, Y. Hou, R. Jiang, L. Sun, Z. Yu, B. Zhang, Y. Huang and Y. Zhang, *J. Mater. Chem. A*, 2019, **7**, 11379–11386.
- B. Ye, R. Jiang, Z. Yu, Y. Hou, J. Huang, B. Zhang, Y. Huang, Y. Zhang and R. Zhang, *J. Catal.*, 2019, **380**, 307–317.
- J.-G. Wang, W. Hua, M. Li, H. Liu, M. Shao and B. Wei, *ACS Appl. Mater. Interfaces*, 2018, **10**, 41237–41245.
- R. Zhang, L. Huang, Z. Yu, R. Jiang, Y. Hou, L. Sun, B. Zhang, Y. Huang, B. Ye and Y. Zhang, *Electrochim. Acta*, 2019, **323**, 134845.
- Y. Huang, L. Sun, Z. Yu, R. Jiang, J. Huang, Y. Hou, F. Yang, B. Zhang, R. Zhang and Y. Zhang, *Catal. Sci. Technol.*, 2020, **10**, 2627–2643.
- F. Li, D. Zhang, R.-C. Xu, W.-F. Fu and X.-J. Lv, *ACS Appl. Energy Mater.*, 2018, **1**, 3929–3936.
- X. Wang, L. Li, Z. Wang, L. Tan, Z. Wu, Z. Liu, S. Gai and P. Yang, *Electrochim. Acta*, 2019, **326**, 134983.
- L. Peng, J. Shen, X. Zheng, R. Xiang, M. Deng, Z. Mao, Z. Feng, L. Zhang, L. Li and Z. Wei, *J. Catal.*, 2019, **369**, 345–351.
- S. Shit, S. Chhetri, S. Bolar, N. C. Murmu, W. Jang, H. Koo and T. Kuila, *ChemElectroChem*, 2019, **6**, 430–438.
- S. Guan, X. Fu, Z. Lao, C. Jin and Z. Peng, *Sustainable Energy Fuels*, 2019, **3**, 2056–2066.
- G. Huang, Z. Xiao, R. Chen and S. Wang, *ACS Sustainable Chem. Eng.*, 2018, **6**, 15954–15969.
- F. Cheng, T. Zhang, Y. Zhang, J. Du, X. Han and J. Chen, *Angew. Chem., Int. Ed.*, 2013, **52**, 2474–2477.
- Y. Li, J. Yin, L. An, M. Lu, K. Sun, Y.-Q. Zhao, D. Gao, F. Cheng and P. Xi, *Small*, 2018, **14**, 1801070.
- Z. Xiao, Y. Wang, Y.-C. Huang, Z. Wei, C.-L. Dong, J. Ma, S. Shen, Y. Li and S. Wang, *Energy Environ. Sci.*, 2017, **10**, 2563–2569.
- X. Yu, Z.-Y. Yu, X.-L. Zhang, P. Li, B. Sun, X. Gao, K. Yan, H. Liu, Y. Duan, M.-R. Gao, G. Wang and S.-H. Yu, *Nano Energy*, 2020, **71**, 104652.
- J. Fu, F. M. Hassan, C. Zhong, J. Lu, H. Liu, A. Yu and Z. Chen, *Adv. Mater.*, 2017, **29**, 1702526.
- X. Liu, S. Min, Y. Xue, L. Tian, Y. Lei and F. Wang, *New J. Chem.*, 2019, **43**, 4152–4159.
- S. Zhao, Y. Wang, J. Dong, C.-T. He, H. Yin, P. An, K. Zhao, X. Zhang, C. Gao, L. Zhang, J. Lv, J. Wang, J. Zhang, A. M. Khattak, N. A. Khan, Z. Wei, J. Zhang, S. Liu, H. Zhao and Z. Tang, *Nat. Energy*, 2016, **1**, 16184.
- Q. Sun, M. Liu, K. Li, Y. Han, Y. Zuo, F. Chai, C. Song, G. Zhang and X. Guo, *Inorg. Chem. Front.*, 2017, **4**, 144–153.
- S. Yadav, S. Sharma, S. Dutta, A. Sharma, A. Adholeya and R. K. Sharma, *Inorg. Chem.*, 2020, **59**, 8334–8344.
- C. Yang, X. Li, L. Yu, X. Liu, J. Yang and M. Wei, *Chem. Commun.*, 2020, **56**, 1803–1806.
- C. Du, Q. Zhang, Z. Lin, B. Yan, C. Xia and G. Yang, *Appl. Catal., A*, 2019, **248**, 193–201.
- S. Hu, X. Chen, Q. Li, Y. Zhao and W. Mao, *Catal. Sci. Technol.*, 2016, **6**, 5884–5890.
- K. Zhu, F. Shi, X. Zhu and W. Yang, *Nano Energy*, 2020, **73**, 104761.
- Y. Zhu, X. Zhong, S. Jin, H. Chen, Z. He, Q. Liu and Y. Chen, *J. Mater. Chem. A*, 2020, **8**, 10957–10965.
- Q. Pan, K. Huang, S. Ni, Q. Wang, F. Yang and D. He, *Mater. Lett.*, 2007, **61**, 4773–4776.
- G. Q. Xu, B. Liu, S. J. Xu, C. H. Chew, S. J. Chua and L. M. Gana, *J. Phys. Chem. Solids*, 2000, **61**, 829–836.
- Z. Qin, K. Xu, H. Yue, H. Wang, J. Zhang, C. Ouyang, C. Xie and D. Zeng, *Sens. Actuators, B*, 2018, **262**, 771–779.
- L. Zhuang, L. Ge, Y. Yang, M. Li, Y. Jia, X. Yao and Z. Zhu, *Adv. Mater.*, 2017, **29**, 1606793.
- J. Bao, X. Zhang, B. Fan, J. Zhang, M. Zhou, W. Yang, X. Hu, H. Wang, B. Pan and Y. Xie, *Angew. Chem., Int. Ed.*, 2015, **54**, 7399–7404.
- Y. Liu, Y. Qiao, G. Wei, S. Li, Z. Lu, X. Wang and X. Lou, *Energy Storage Mater.*, 2018, **11**, 274–281.
- L. Ji, B. Wang, Y. Yu, N. Wang and J. Zhao, *Electrochim. Acta*, 2020, **331**, 135348.
- Y. Tang, F. Jing, Z. Xu, F. Zhang, Y. Mai and D. Wu, *ACS Appl. Mater. Interfaces*, 2017, **9**, 12340–12347.
- X. Hu, X. Sun, Q. Song, Y. Zhu, Y. Long and Z. Dong, *Green Chem.*, 2020, **22**, 742–752.

- 37 C. Yu, Z. Liu, X. Meng, B. Lu, D. Cui and J. Qiu, *Nanoscale*, 2016, **8**, 17458–17464.
- 38 Y. Pan, K. Sun, S. Liu, X. Cao, K. Wu, W.-C. Cheong, Z. Chen, Y. Wang, Y. Li, Y. Liu, D. Wang, Q. Peng, C. Chen and Y. Li, *J. Am. Chem. Soc.*, 2018, **140**, 2610–2618.
- 39 L. Yang and L. Zhang, *Appl. Catal., A*, 2019, **259**, 118053.
- 40 L. Liu, J. Sun, J. Ding, Y. Zhang, T. Sun and J. Jia, *Inorg. Chem.*, 2019, **58**, 13241–13249.
- 41 S. Jaiswar and K. D. Mandal, *J. Phys. Chem. C*, 2017, **121**, 19586–19601.
- 42 Y. P. Zhu, T. Y. Ma, M. Jaroniec and S. Z. Qiao, *Angew. Chem., Int. Ed.*, 2017, **56**, 1324–1328.
- 43 C. Wang, X.-D. Zhu and P.-J. Zuo, *Chem. Eng. J.*, 2020, **396**, 125163.
- 44 J. Chen, J. Cong, Y. Chen, Q. Wang, M. Shi, X. Liu and H. Yang, *Appl. Surf. Sci.*, 2020, **508**, 145239.
- 45 X. Gao, B. Wang, Y. Zhang, H. Liu, H. Liu, H. Wu and S. Dou, *Energy Storage Mater.*, 2019, **16**, 46–55.
- 46 Y. Wang, Z. Zhang, X. Liu, F. Ding, P. Zou, X. Wang, Q. Zhao and H. Rao, *ACS Sustainable Chem. Eng.*, 2018, **6**, 12511–12521.
- 47 Y. Lu, L. Su, J. Qi, S. Lei, B. Liu, Q. Zang, S. Shi and X. Yan, *J. Mater. Chem. A*, 2018, **6**, 13717–13724.