



Cite this: *Green Chem.*, 2024, **26**, 5386

Mechanochemical and aging-based reductive amination with chitosan and aldehydes affords high degree of substitution functional biopolymers†

Galen Yang, ^{‡a} Sophie Régnier,^b Noah Huin,^a Tracy Liu,^a Edmond Lam ^{*‡a,b} and Audrey Moores ^{*‡a,c}

Chitosan is readily available from various biomass waste streams including crustaceans, cephalopods, insects, and fungus. The polymer possesses primary amine groups which are great handles for functionalization. Yet efficient functionalization with high degree of substitution is challenging to achieve *via* solvothermal methods due to limitations in chitosan solvation properties. Herein we report a mechanochemical and aging-based method directly addressing this point. Working in the solid phase helps stabilize the formation of Schiff bases from chitosan and aldehydes, affording a novel pathway to the green functionalization of chitosan by reductive alkylation, with unprecedentedly high degrees of substitution. The method showed great efficacy and compatibility for chitosan to be functionalized with 21 different aldehyde substrates and a low process mass intensity (PMI) of 36. This work also opens a new avenue for the development of mechanochemical and aging-based reductive amination transformations.

Received 11th January 2024,
Accepted 18th March 2024

DOI: 10.1039/d4gc00127c

rs.c.li/greenchem

Introduction

Chitin is the second most abundant biopolymer and the most abundant nitrogen-containing biopolymer.¹ Besides the great availability of polysaccharides, this class of natural polymers is also biodegradable and biocompatible, which makes it ideal for high-value biomedical applications.^{2,3} Chitin and its deacetylated derivative chitosan (Chs) can be extracted from various biomass waste streams, including crustaceans, cephalopods, insects, and fungi on a large scale annually.⁴ The primary amine groups of Chs not only impart unique antimicrobial ability on the biopolymer,^{5,6} but permits important chemical modifications for the introduction of new, tailor-made structures.^{7–9}

Amines are amenable to a wide range of organic transformations, such as reactions with acyl halide,¹⁰ sulfonyl chlorides,¹¹ and alkyl halides.¹² The coupling of amines with aldehydes to form Schiff bases¹³ is a popular and versatile functionalization approach. When subjected to subsequent reduction, Schiff bases form stable substituted amines and enamines, in an overall pathway called reductive amination.¹⁴ Despite these prospects, Chs functionalization faces several limitations, the most serious one being its poor solubility in most media.^{15,16} Indeed, while Chs dissolves well in aqueous acidic media, side reactions including Chs hydrolysis occurs under these conditions.^{17,18} Additionally, aqueous solutions of Chs also tend to feature high viscosity, reducing mixability and processability,^{19,20} a problem that restricts the feasibility of some Chs chemical modifications. These complications are a shared conundrum in polysaccharide functionalization, leading to a common necessity of using harsh reaction conditions or using excess reagents to accomplish the target processes,^{21–23} impairing the competitiveness of natural polymers against synthetic polymers.^{24–26}

Mechanochemistry is an emerging synthetic methodology^{27–30} which utilizes mechanical force to trigger chemical phenomena. It has been shown to reduce or eliminate the need for auxiliary substrates such as solvent, accelerate chemical reaction,³¹ reduce energy requirement³⁰ and even afford reactivity and selectivity that have not been observed in solution-based chemistry.^{29,32} Besides reactions happening

^aCentre in Green Chemistry and Catalysis, Department of Chemistry, McGill University, 801 Sherbrooke St. West, Montreal, QC, H3A 0B8, Canada.

E-mail: Audrey.moores@mcgill.ca

^bNational Research Council Canada, Aquatic and Crop Resource Development Research Centre, 6100 Royalmount Avenue, Montreal, Quebec H4P 2R2, Canada

^cDepartment of Materials Engineering, McGill University, 3610 University Street, Montreal, Quebec H3A 0C5, Canada

†Electronic supplementary information (ESI) available: Additional methods information, and original spectroscopic data. See DOI: <https://doi.org/10.1039/d4gc00127c>

‡Present addresses: Centre in Green Chemistry and Catalysis, Department of Chemistry, McGill University, Montréal, Québec H3A 0B8, Canada

during mechanical treatment, the concept of aging has been introduced, in which reactions occur in the solid phase after an initial mixing phase.³³ These solid-state methodologies are well suited in the context of biomass conversion and polysaccharide functionalization, especially as such starting materials tend to be insoluble,³⁴ as demonstrated with chitin extraction,^{35,36} and conversion.^{36,37} Our group has developed a workflow using the combination of mechanochemistry and aging to extract chitin from crustacean wastes;³⁵ deacetylate chitin into Chs;³⁸ and hydrolyze Chs to achieve controlled molecular weight.³⁹ Similarly, Van Poucke *et al.* recently reported a synthesis of water-soluble *N*-sulfonated Chs by mechanochemistry.⁴⁰

Imine, or Schiff-base (SB), formation is one of the most studied functionalization of Chs and has led to applications that harness its bioactivities,^{41–45} capability as catalyst support for chemical synthesis,^{46–48} ability to absorb heavy metal ions,⁴⁹ and sensing capability.⁵⁰ The conventional synthesis of a Chs SB relies on the dissolution of Chs in an acetic acid solution or suspension in alcohol under reflux conditions.^{51–53} Although stoichiometric amount of aldehydes were used in these reactions, the formation of SB was not quantitatively reported in term of degree of substitution (DS).^{42–44,46–50} Mechanochemistry offers an interesting approach to SB synthesis,⁵⁴ as illustrated by the example of Crawford *et al.* who reported the synthesis of a diamine from 4,4'-oxydianiline and 2 equivalents of *ortho*-vanillin by either ball milling or twin-screw extrusion.⁵⁵ More recently, Fatika *et al.* reported a simple solid-state synthesis of air stable Chs SB *via* solvent-free mechanochemical grafting with a scope of three benzaldehyde derivatives.⁵⁶

A SB is inherently unstable under acidic conditions and will regenerate into its carbonyl and the amine components.^{57,58} One simple yet effective strategy to solve this instability is to reduce the imine into an alkylated amine.⁵⁹ This process, the reductive amination (reductive alkylation from the perspective of the amine), ensures access to a compound able to withstand a much broader range of chemical conditions.^{60,61} In general, reductive amination is also proposed as a greener way of making substituted amines since it avoids the use of reactive and potentially genotoxic alkylating reagents that are used in traditional S_N2-type reactions.^{62,63} Reductive alkylation has been employed as an effective way to functionalize Chs to valuable materials.^{64–67} Bobu *et al.* reported a solution-based method to functionalize Chs with octanal into *N*-alkyl Chs *via* reductive amination, albeit with a low DS of 0.03, towards paper-making applications.⁶⁸ In that sense, mechanochemistry appears as an exciting opportunity to improve Chs reductive alkylation and access higher levels of DS.

Herein we report a mechanochemical and aging-based approach to alkylate Chs *via* reductive amination, with a wide scope of functionalities. The resulting materials feature excellent stability. We investigated the kinetics of the solid-state SB formation and reduction by sodium borohydride (NaBH₄) *via* aging. We also examined the versatility of this method with a range of carbonyl compounds from aromatic to aliphatic aldehydes.

The method also allows for the production of Chs derivatives inaccessible by solvothermal methods. We characterized the special properties of some Chs derivatives and suggested potential applications for the materials. More importantly, we evaluated this method with green metrics and demonstrated that our process features improved process mass intensity (PMI) as compared to solution-based methods. This work is also a proof of concept of the deployment of reductive amination methodology through mechanochemistry and aging.


Results and discussion

Mechanochemical synthesis of chitosan furfural Schiff-bases with a mixer mill

We first explored the preparation of Chs SB using furfural (a model aldehyde) by means of liquid-assisted grinding (LAG) mechanochemistry.⁶⁹ A Retsch MM 400 mixer mill equipped with polytetrafluoroethylene (PTFE) SmartSnap grinding jars (15 mL) and one 7 mm zirconia ball in each jar was fitted with Chs and 1 equivalent of furfural (based on Chs primary amine units). As the process was optimized, we found that LAG favored the reaction, so we used 50 μL of deionized (DI) water and a milling time of 30 min under 29.5 Hz (Scheme 1). After set milling time, the reaction mixture was dispersed, washed, and filtered in ethanol (EtOH) and water before being dried.

The resulting sample (**1**) was characterized by Fourier transform infra-red (FT-IR) spectroscopy, ¹³C magic angle spinning nuclear magnetic resonance (ssNMR) and ¹H NMR. The appearance of a medium intensity peak at 1645 cm⁻¹ was consistent with a C=N stretching absorption (see ESI† for complete characterization). The ¹³C ssNMR spectrum revealed the appearance of new peaks, especially one at 148.16 ppm characteristic of an imine carbon, as well as peaks for the introduction of a furan ring structure. Both FT-IR (Fig. S1†) and ¹³C ssNMR (Fig. S2†) were consistent with the formation of the desired compound **1**.

Sample **1** was readily soluble at 1 wt% in 0.1% HCl solution, like untreated starting Chs, providing a homogeneous, viscous, and clear solution with a slight yellow hue. Solution state ¹H NMR in 0.1% HCl in D₂O was performed on **1** to calculate the degree of imination on Chs primary amine and the % conversion of the furfural as a reagent (see Fig. 1). Importantly, the starting Chs featured 23% acetylated monomers (calculated with ¹³C ssNMR), which cannot undergo SB formation and thus were used as an internal standard throughout this study for aldehyde % conversion and Chs degree of imination (see discussion in ESI†). ¹H NMR of **1** revealed the presence of free furfural at 9.49 (a), 7.90 (b), 7.56 (c), and 6.75 ppm (d), and a set of four broad peaks at 8.80 (a₁), 8.25 (b₁), 7.98 (d₁), and 6.99 ppm (c₁), all with intensity at about 30% of the free furfural peaks. Together, the number and values of chemical shifts in this group, and the integration pattern confirm the formation of a **1**. Overall, we measured 62.5% of free furfural and 34.3% of **1** (mass balance = 96.8%).

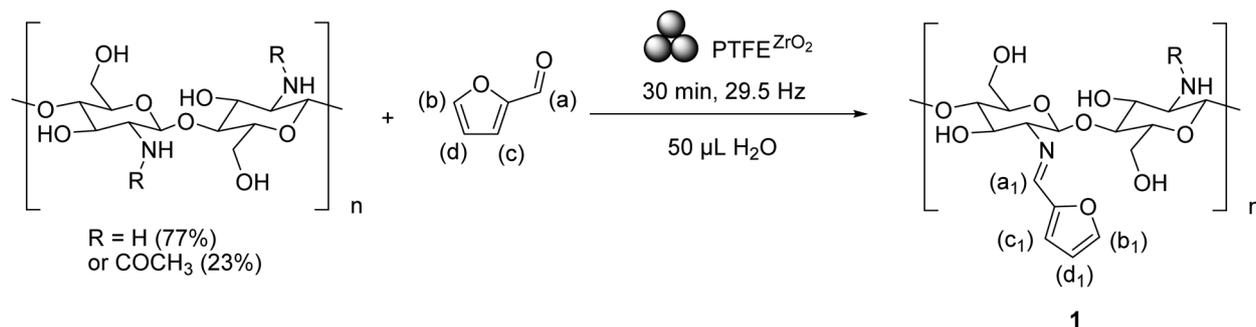

Scheme 1 Mechanochemical synthesis of chitosan furfural SB (**1**). Typical experimental conditions: Chs (250 mg), 1 eq. of furfural (95.0 mg) were loaded into a PTFE jar with a 7 mm ZrO_2 ball and milled for 30 min at 29.5 Hz in LAG condition with H_2O (50 μL).

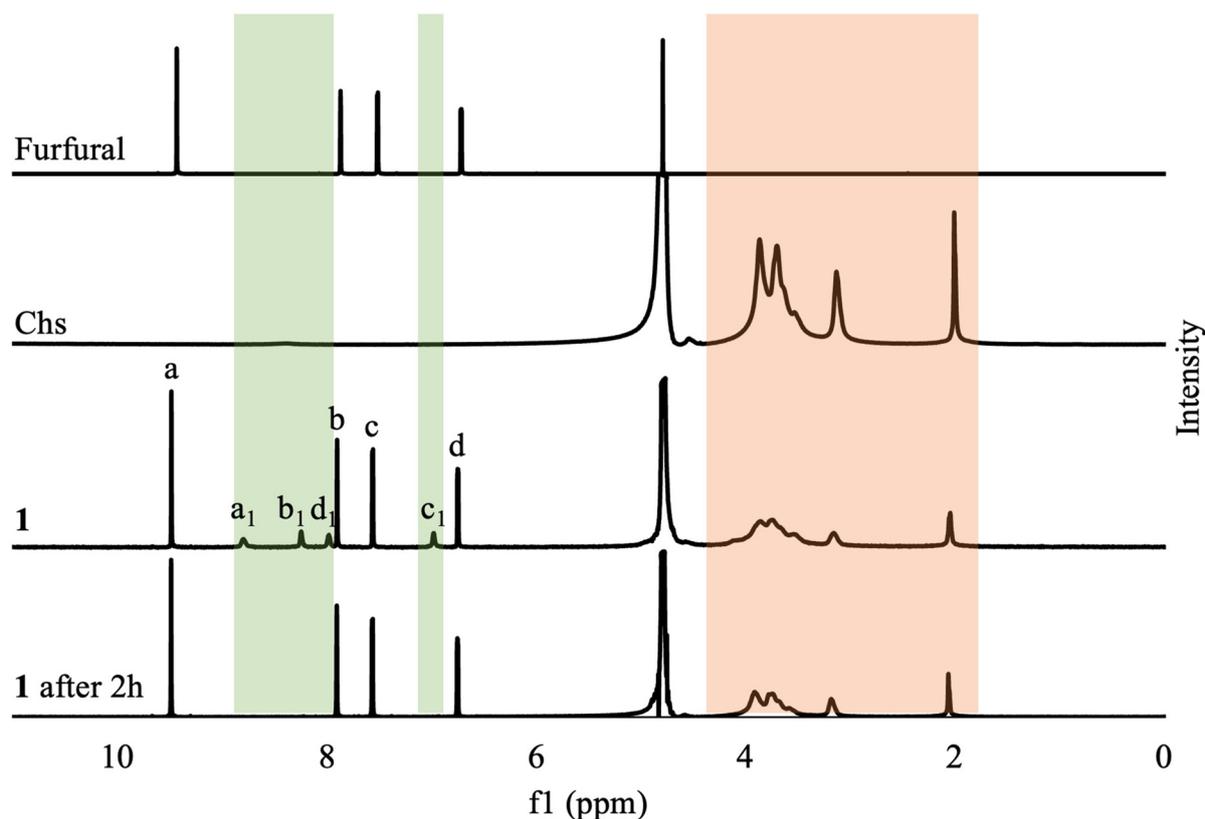


Fig. 1 ^1H NMR spectra (0.1% HCl in D_2O) of furfural, Chs, **1** and **1** after 2 h in solution. Peaks characteristic of the imine-bound furan ring are highlighted in green and peaks characteristic of the chitosan backbone are highlighted in orange.

A second ^1H NMR spectrum was taken on the same NMR sample after 2 h and a complete disappearance of **1** was observed, with all the furfural type peaks being from free furfural (mass balance = 96.9%).

This analysis confirms that the condensation of a stoichiometric amount of furfural onto Chs was successful, although incomplete, and that under mildly acid liquid conditions (pH 5.5, RT), SB **1** is unstable and hydrolyzes back into free Chs and furfural. This instability is detrimental to the applicability of Chs SB because most applications would require a step of sample dissolution for dispersion or permeation. In those

scenarios, the Chs SB would lose the desired properties obtained from the chemical modification and generate potentially hazardous free carbonyl compounds. This also explains why many synthetic methods rely on excess amounts of reagents to achieve Chs SB functionalization in a solution.^{42,43,46,49,52,53}

Mechanochemical reductive alkylation of chitosan with furfural and NaBH_4

One simple yet effective strategy to solve the SB instability conundrum is to reduce the imine into an alkylated amine, which


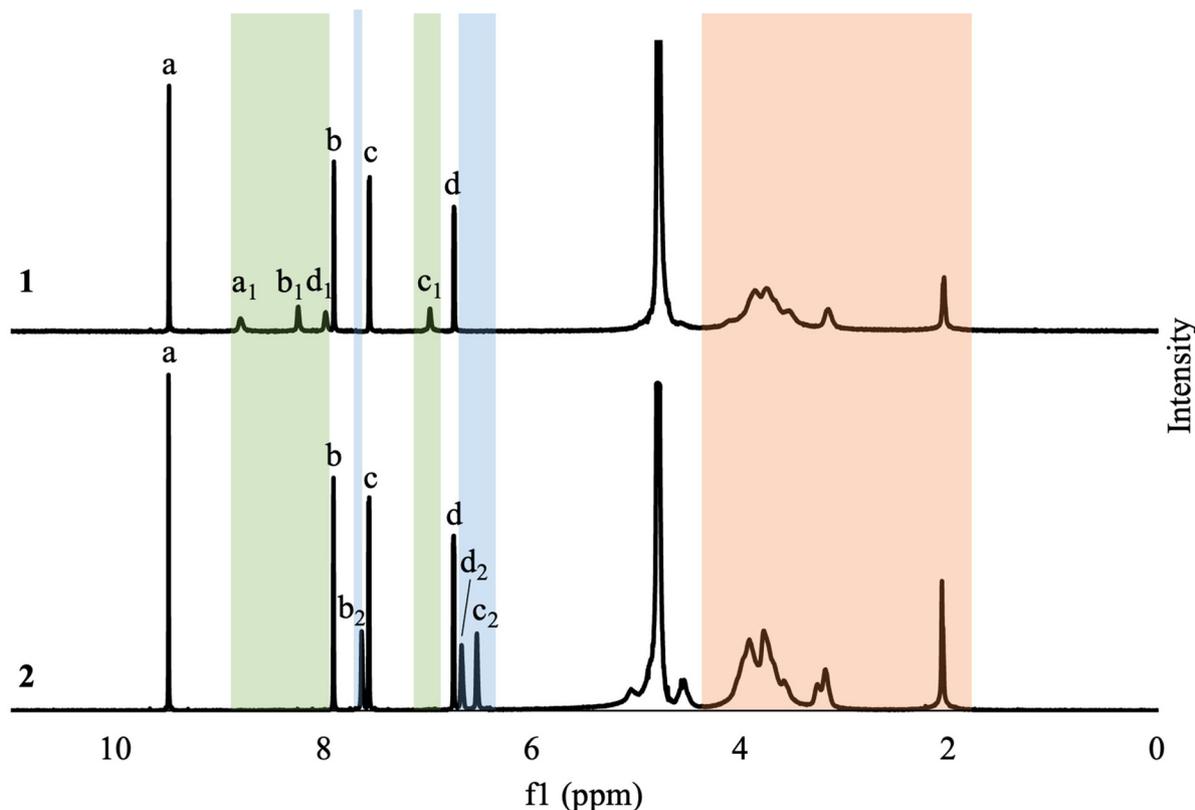


Fig. 2 ^1H NMR spectra (0.1% HCl in D_2O) of **1** and **2** from mechanochemical reduction with NaBH_4 in solution. Peaks characteristic of the imine-bound furan ring are highlighted in green; peaks characteristic of the amine-bound furan ring are highlighted in blue and peaks characteristic of the chitosan backbone are highlighted in orange.

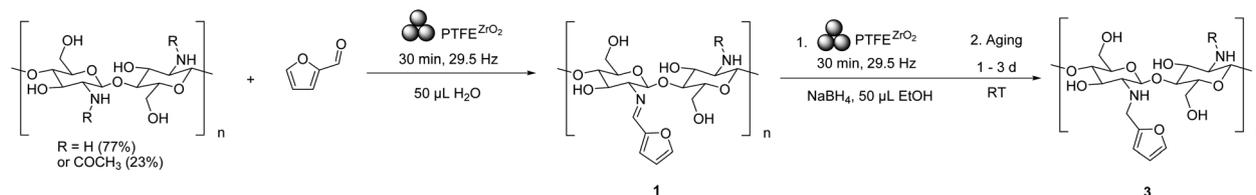

Scheme 3 Mechanochemical and aging-based reductive alkylation of Chs with NaBH_4 towards high DS **3**. Typical experimental conditions for the aging step: NaBH_4 and **1** reaction mixture were transferred to a sealed vial and aged for 1, 2, or 3 d at room temperature.

ing near complete DS, distinguishing **3** from **2**, in which the functionalization resulted in a mixture of SB and reduced amine. The method eliminated the repeated dissolution, refluxing, and pH adjustment steps that were widely employed in previously reported solution-based methods of similar modifications.^{64–67} The mechanism behind this aging-extended **1** NaBH_4 reduction was likely due to a homogeneous mixing and activation introduced by ball milling, followed by a continuance of the reaction during aging under ambient conditions.

The role of LAG solvent in mechanochemical and aging-based **3** reduction with NaBH_4

The use of water in the LAG condition was crucial for the mechanochemical synthesis of **1** and consequently **3**.

Although SB formation is a condensation reaction and prefers anhydrous reaction conditions in the liquid phase,^{71,72} the presence of catalytic amounts of water was key to introduce reactivity to the system under mechanochemical conditions. This effect was tested by varying LAG conditions during the Chs furfural SB formation step (from starting material to **1**, Scheme 3) while the LAG condition (50 μL EtOH) in the second step (formation of **3**) was kept constant (see Table 2). The reaction between Chs and furfural, in absence of LAG water solvent, only led to 13.3% DS in **3**, which was significantly lower than the one achieved with LAG condition of 99.1% (see Table 1). For further investigation, Chs was pre-dried at 117 $^\circ\text{C}$ to remove the 8.03% of water present in Chs as received from supplier, as measured by thermogravimetric

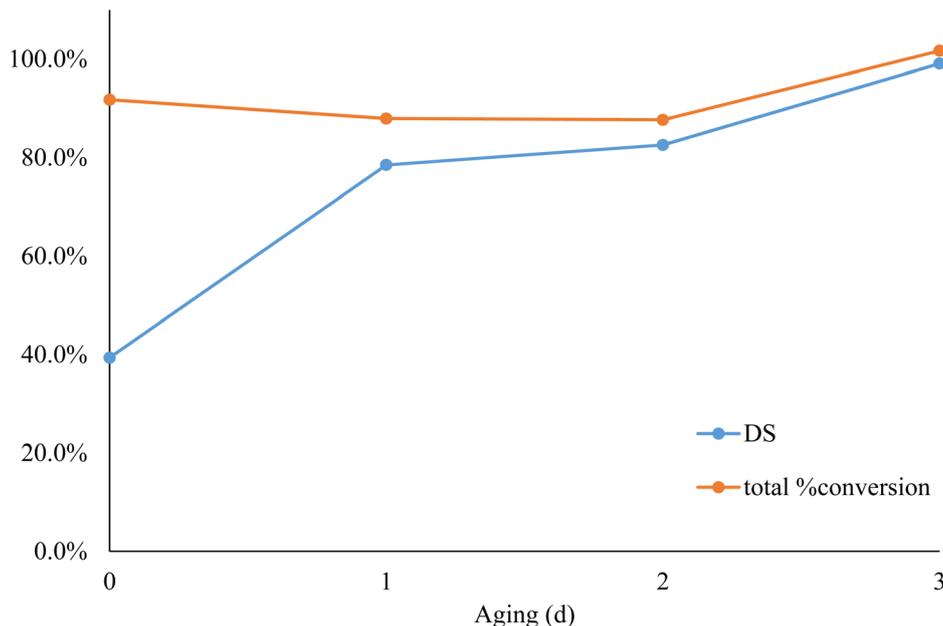


Fig. 3 Effect of aging time on the DS and total % conversion of furfural toward the product **3**. Typical experimental conditions: reaction mixture was transferred to a sealed vial and aged for 1, 2, or 3 d at room temperature.

Table 1 The effect of LAG solvent in mechanochemical and aging-based **3** reduction with NaBH_4 .

Chs starting material	LAG solvent	Chs %DS
Chs	Water (50 μL)	99.1
Chs	none	13.3
DChs	none	9.0
DChs	Water (20 μL)	17.0
DChs	Water (20 + 50 μL)	90.0
DChs	EtOH (20 μL)	19.0
DChs	EtOH (20 + 50 μL)	40.0

analysis (TGA). The pre-dried Chs (DChs) and furfural reaction yielded even lower DS of 9.0%. Experiments were also conducted in which an equivalent of amount of water (20 μL) removed from Chs upon drying was added back to the DChs. This resulted in a comparable 17.0% DS to the experiment with Chs from the vendor bottle. Only when removed water was added back to dried Chs with the addition of the 50 μL LAG water, did a good DS of 90.0% was achieved.


The effect of LAG solvent was also studied by substituting water with EtOH. An equal volume of EtOH was used to replace the removed water from DChs and the experiment yielded 19.0% DS. When an additional 50 μL EtOH was added to the already present EtOH content, a 40.0% DS was measured, showing poorer results than with LAG water. This investigation revealed water as the optimal LAG solvent over EtOH in the mechanochemical synthesis of **1**. The enhancement came from improved mobility for furfural molecules to diffuse into the Chs. Further experiments of substituting water with EtOH as the LAG solvent also promoted reactivity to 40.0% DS but was not as effective as water reaching 90.0% DS.

The enhanced performance of water over EtOH as LAG solvent could stem from water acting as a Lewis acid, which is required for the protonation of the aldehyde to activate the nucleophilic attack of the primary amine of Chs. Such interaction is the key step in hemiaminal intermediate formation in the SB condensation. In contrast, EtOH is a Lewis base, incapable of protonating the aldehyde (Scheme S2[†]). As a result, the introduction of EtOH as a LAG solvent could only facilitate **1** formation through the enhancement of diffusion and was found less effective compared to water.

The aldehyde scope of the mechanochemical and aging-based chitosan reductive alkylation

Finally, we explored the versatility of this reported mechanochemical and aging-based Chs reductive alkylation functionalization by performing experiments on Chs with aldehyde compounds (see Scheme 4 and Table 2). The least amount of milling (30 min in each step) was selected to minimize the process's energy consumption and avoid comminution or undesired side reactions caused by increased temperature. A relatively long aging of 3 d was performed to achieve high reaction conversion and to reduce waste from unreacted reagents.

The versatility and robustness of this mechanochemical and aging-based Chs reductive alkylation were investigated with a series of furfural derivatives, aliphatic aldehydes, and aryl aldehydes. The samples followed the mechanochemical and aging-based chitosan reductive alkylation with the selected scope of aldehydes were characterized in DS and isolated yield (see ESI[†] for calculation). There was only a small loss of samples in isolation and purification thanks to the omission of dissolution and precipitation in the procedure. In

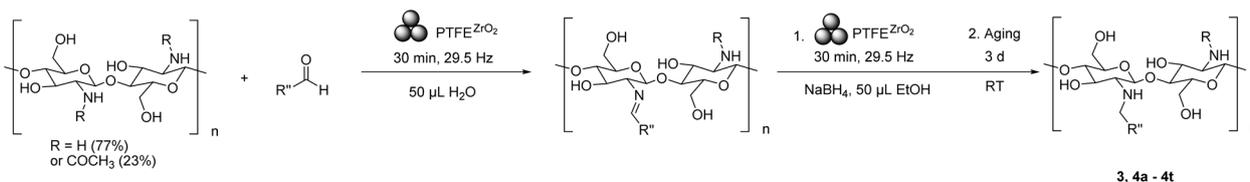

Scheme 4 The generic scheme of the mechanochemical and aging-based reductive alkylation of Chs into **3**, **4a–4t** with aldehyde R''CHO (see Table 2 for scope). Typical experimental conditions: Chs (250 mg), 1 eq. of aldehyde compound **a–t** (0.99 mmol), and H₂O (50 µL) are loaded into a PTFE jar with a 7 mm ZrO₂ ball and milled for 30 min at 29.5 Hz. This was followed by the loading of 1 eq. of NaBH₄ (32.4 mg) and EtOH (50 µL) into the PTFE jar containing the reaction mixture and milled for 30 min, and the sample mixture was transferred to a sealed vial and aged for 3 d at room temperature.

Table 2 Scope of mechanochemical and aging-based chitosan reductive alkylation experiment using different carbonyl compounds. Spectra are presented in Fig. S4.a to S4.t†

Aldehyde (R''CHO)	Chs %DS	% Isolated yield
Furfural	99.1	77.2
a 5-(Hydroxymethyl)furfural	58.6	86.5
b 5-(1,2-Dioxolan-4-yl)furan-2-carbaldehyde	83.0	74.1
c Isobutylaldehyde	38.4	74.5
d Pentanal	Virtually 100.0	80.6
e Hexanal	Virtually 100.0	76.2
f Heptaldehyde	Virtually 100.0	73.6
g Cyclohexanecarboxaldehyde	97.2	76.1
h Octanal ^a	91.1	81.6
i Nonanal ^a	22.4	90.6
j Undecanal ^a	12.0	97.1
k Benzaldehyde	93.2	77.2
l 4-Hydroxybenzaldehyde	64.5	85.6
m 3,4-Dihydroxybenzaldehyde	41.2	87.5
n 2-Chlorobenzaldehyde	47.3	92.3
o 3-Bromobenzaldehyde	45.7	97.8
p 4-Bromobenzaldehyde	9.0	95.6
q 4-(Dimethylamino)benzaldehyde	7.6	88.4
r 2-Pyridinecarboxaldehyde	66.6	99.0
s 4-Nitrobenzaldehyde	4.7	94.6
t 2-Hydroxy-1-naphthaldehyde	N/A	74.2

^a Determined by ¹³C ssNMR.

general, the isolated yield of samples, i.e. the percentage of recovered chitosan backbone, falls between 73.6 to 99.0%. Results revealed that the method worked well on furfural derivatives including 5-(hydroxymethyl)furfural (**a**) and synthesized 5-(1,2-dioxolan-4-yl)furan-2-carbaldehyde (**b**) without deprotecting the acetal group, with DS of 58.6% and 83.0% respectively. The reductive alkylation reaction between Chs and aliphatic aldehydes performed the best with aliphatic aldehydes consisting of alkyl chains or rings with 4–6 hydrocarbons. The calculated DS for **4d**, **4e**, and **4f** were even slightly over 100% due to the intrinsic inconsistency of the starting Chs, thus the reductive alkylation with these aldehydes were seen as virtually complete. The cyclic structure of cyclohexanecarboxaldehyde (**g**) did not hinder the reaction as it still induced a high 97.2% DS. With isobutylaldehyde (**c**), octanal (**h**), nonanal (**i**), and undecanal (**j**), the DS from the

reaction was significant but not as high as for other examples, ranging from 12.0 to 91.1%. Remarkably though, the properties of resulting alkylated Chs were significantly affected by this functionalization. The modification with aldehydes which have straight alkyl chains with more than 7 carbons significantly increased hydrophobicity of the materials, and samples **4h**, **4i**, and **4j** were not soluble in the aqueous NMR solvent of 0.1% HCl acidified D₂O. Thus, the characterization and DS calculations were carried out by ¹³C ssNMR, which confirmed the successful reaction, while more destructive techniques and conditions were explored to assist in acquiring ¹H NMR spectra of the samples for more quantitative analysis (see discussion in ESI†). The long-chain aldehydes have a lower affinity with water, which could inhibit the protonation of the aldehydes by water, leading to lower DS as a result. Another factor of the low DS could be attributed to the poor diffusion of long-chain aldehydes onto Chs to enable the nucleophilic attack of Chs amine to the aldehyde substrates. Another interesting example is 4-(dimethylamino)benzaldehyde (**q**). Despite a low DS of 7.62%, **4q** dissolves in DI water, affording a basic solution at pH 12. It is unusual for chitosan derivatives to be soluble at high pH, and this method complements the mechanochemical *N*-sulfonation of Chs as reported by Van Poucke *et al.*⁴⁰ The completely distinct solvation properties of **4h**, **4i**, **4j** to **4q** suggested the reductive alkylation approach offers a powerful means for manipulating the properties of Chs such as solvation properties. Chs could be tailored to specific properties with only relatively conservative levels of DS

Finally, the reductive alkylation of Chs with aryl aldehydes was largely affected by the substituents. Benzaldehyde (**k**) afforded an excellent DS of 93%, as well as 2-pyridinecarboxaldehyde (**r**) with 66.6% DS. Electron donating groups *para*-substituted to the benzaldehyde (such as 4-hydroxybenzaldehyde, **l**) or electron withdrawing groups *meta*-substituted to the benzaldehyde (3-bromobenzaldehyde, **o**) seemed to favor good results with DS in the 45 to 65% range. *Ortho* substitution and disubstitution gave an average result with 3,4-dihydroxybenzaldehyde (**m**) and 2-chlorobenzaldehyde (**n**) affording results in the upper 40% range. With electron withdrawing groups *para*-substituted to benzaldehydes such as 4-bromobenzaldehyde (**p**) and 4-nitrobenzaldehyde (**s**), reaction efficiency was reduced to single digit DS, due to the reduced electron density on aldehyde oxygen inhibited its protonation. The *para*-substi-

tuted 4-(dimethylamino)benzaldehyde (**q**) did not provide a much better DS with 7.6%, although as mentioned above, the solvation property changes are quite drastic. 2-Hydroxy-1-naphthaldehyde (**t**) did not show any conversion, possibly because of the bulkiness of the naphthyl group.

Advantages of the method

We compared our novel mechanochemical and aging-based Chs reductive alkylation to the conventional solution-based methods,^{68,73,74} and to the solventless mechanochemical method for Chs SB recently reported by Fatika *et al.*⁵⁶ In the perspective of the chemical bond formed in the current study and previously reported methods, our method allowed for more robust Chs functionalization compared to the mechanochemically synthesized Chs SB, affording alkylated Chs derivatives free from imine hydrolysis risk. When comparing our method to other Chs reductive alkylation systems, the present method does not require Chs dissolution in acidic aqueous media, providing a number of advantages: (1) this allows the functionalization on Chs to occur with acid-sensitive compounds as demonstrated with 5-(1,2-dioxolan-4-yl)furan-2-carbaldehyde (**b**) and (2) SB formation equilibrium is not favored under acidic conditions, meaning that when the reducing agent is added, only a fraction of the aldehyde is engaged in an imine bond, explaining the low DS reported before. A good example of this is provided with octanal (**h**), for which the mechanochemical and aging-based Chs reductive alkylation process achieved high DS at 49.3% compared to only 0.03% in the solution-based method reported by Bobu *et al.*⁶⁸ In the work of Rabea *et al.* *N*-(butyl)chitosan (**4d**) was prepared by a similar solution-based approach.⁶⁷ With 1 : 1 mol ratio of pentanal (**d**) to Chs primary amine, they only achieved a DS of 36% compared to virtually 100% by our proposed method.⁶⁷ Thus, the current method can perform similar chemical reactions with higher atom economy, reflected by the higher DS reported. The elimination of solvent in the reaction and simplification of the workup procedure also led to an impressively reduced calculated PMI of 36 (with furfural, 3) compared to 1300 calculated based on available information by Bobu's study and 602 from Rabea's study.^{67,68}

Conclusion

In this study, we present a method to functionalize Chs by alkylation in the solid state *via* reductive amination by mechanochemical ball-milling combined with aging under ambient conditions. With water LAG conditions, Chs can form a SB with series of aldehyde compounds, followed by mechanochemical reduction by NaBH₄ under EtOH LAG conditions to yield alkyl-Chs substituted on the amine Chs groups. The method enabled efficient reductive alkylation on Chs with furfural at 99.1% DS, close to total functionalization of the available Chs amine groups. A scope investigation proved the robustness and versatility of the presented method compatible with a wide range of both aliphatic and aromatic aldehydes.

The mechanochemical approach eliminated the dissolution of Chs and allowed for the reaction to occur with aldehyde reagents that are unstable in solution. This method is simpler with reduced reaction substrates and steps leading to an impressively low PMI of 36. It affords Chs with new solvation properties. In conclusion, the mechanochemistry and aging-based reductive amination/alkylation of Chs provides a new avenue to design and effectively functionalize Chs into value-added material for applications such as bio-sensing, medication, food, cosmetic, and fibre making.

Experimental

Materials

Chitosan (from shrimp shell, practical grade), furfural (99%), 5-(hydroxymethyl)furfural ($\geq 99\%$, FG), benzaldehyde (*ReagentPlus*®, $\geq 99\%$), 4-hydroxybenzaldehyde (98%), 3,4-dihydroxybenzaldehyde (97%), 2-chlorobenzaldehyde (99%), 3-bromobenzaldehyde (97%), 4-bromobenzaldehyde (*ReagentPlus*®, 99%), 4-(dimethylamino)benzaldehyde (ACS reagent, 99%), 2-pyridinecarboxaldehyde (99%), 4-nitrobenzaldehyde (98%, GC), 2-hydroxy-1-naphthaldehyde (technical grade), isobutyraldehyde ($\geq 99\%$), hexanal (98%), cyclohexanecarboxaldehyde (97%), heptaldehyde (95%), octanal (99%), nonyl aldehyde (95%), undecyl aldehyde (97%), sodium borohydride (99%) and deuterium oxide (99.9% D) were purchased from Sigma-Aldrich Co. L.L.C. (St. Louis, MO, USA). Pentanal (97%) and hydrochloric acid were purchased from Fischer Scientific L.L.C. (Ottawa, ON, Canada). EtOH for work-up and washing was purchased from Commercial Alcohols by Greenfield Global (Brampton, ON, Canada). For solution-state NMR characterization, 0.1% HCl acidified D₂O was used to dissolve modified chitosan samples.

Milling

In the following procedures, a Retsch MM 400 mixer mill was used, with polytetrafluoroethylene (PTFE) SmartSnap Jars (15 mL) manufactured by Form-Tech Scientific (Canada), equipped with 7 mm balls made of zirconia.

Mechanochemical-based chitosan SB experiments

In a typical experiment, 250 mg of Chs with 1 equivalent of aldehyde to the glucosamine units were combined in the PTFE grinding jars and milled under a LAG condition with the addition of 50 μ L of DI water for 30 min with one 7 mm zirconia ball.

Mechanochemical and aging-based chitosan SB reduction experiments

In a typical experiment, the reaction mixture of Chs SB was combined with 1 equivalent of NaBH₄ in the same PTFE grinding jars and milled under a new LAG condition with the addition of 50 μ L of EtOH for 30 min with the same 7 mm zirconia ball. After milling, the reaction mixture was transferred into a sealed vial and aged for 3 d at RT. Following milling and

aging, the reaction mixture was dispersed and washed in EtOH (40 mL), filtered, and washed repeatedly with DI water (80 mL) to remove all excess reagents, reaction by-products, and EtOH from the Chs samples during the first washing step. Finally, samples were collected and dried overnight in a vacuum oven at 50 °C for storage and characterization. The final alkylated Chs samples are fine powders with colours determined by the aldehyde used in the experiments. The same work-up procedure can also be applied after the mechanochemical-based Chs SB experiments to yield chitosan imine intermedia for reaction kinetic studies.

Analysis – characterization – equipment details and methods

¹³C magic angle spinning nuclear magnetic resonance (MAS-NMR). NMR spectra were recorded on a Varian VNMRs operating at 400 MHz for the solid-state ¹³C acquisition using a 4 mm double-resonance Varian Chemagnetics T3 probe. A contact time of 1000 μs and a recycle delay of 3 s were used to acquire quantitative spectra. Five hundred scans were acquired of each sample for a total time of 1.5 h.

¹H NMR. NMR spectra were recorded on a Varian VNMRs spectrometer operating at 500 MHz for ¹H acquisitions with 0.1% HCl D₂O solution as solvent. The DS was calculated based on the intensities of emerging peaks as a result of Chs functionalization by reductive alkylation, and their ratio to that of the CH₃ peak of chitosan acetamide made quantifiable with the average degree of deacetylation (DDA) of Chs starting material. The reaction conversion of Chs SB was also calculated based on the amount of amine grafted peaks and the regenerated free aldehyde peaks from the imine hydrolysis in the acidic NMR solvent.

FT-IR spectral analysis. The Chs SB imine evolution and the C–N bond formation after mechanochemical and aging-based chitosan SB reduction was monitored using the Fourier transmission infrared (FT-IR) infrared spectrometer Alpha II from Bruker Germany. Experimental spectra were acquired at 4000 to 400 cm⁻¹ at the best resolution of 0.5 cm⁻¹, with an attenuated total reflectance (ATR) accessory, a single bounce diamond crystal, and a standard, room-temperature LiTaO₃ (lithium tantalate) MIR detector.

TGA. TGA analysis was performed on a Discovery 5500 from TA Instruments under nitrogen with balance flow rate at 10 mL min⁻¹ and sample flow rate at 25 mL min⁻¹. The temperature was raised from room temperature to 800 °C at ramp rate of 10 °C min⁻¹.

Abbreviations

Chs	Chitosan
EtOH	Ethanol
SB	Schiff base
NaBH ₄	Sodium borohydride
PMI	Process mass intensity
LAG	Liquid-assisted grinding
PTFE	Polytetrafluoroethylene

DI	Deionized
FT-IR	Fourier transform infra-red
ssNMR	Magic angle spinning nuclear magnetic resonance
DS	Degree of substitution
TGA	Thermogravimetric analysis

Author contributions

The manuscript was written through the contributions of all authors. All authors have given approval to the final version of the manuscript.

Conflicts of interest

There is no conflict to declare.

Acknowledgements

We thank the Natural Science and Engineering Research Council of Canada (NSERC) – Discovery Grant and Discovery Accelerator Supplement, the Canada Foundation for Innovation (CFI), the Fonds de Recherche du Québec – Nature et Technologies (FRQNT) – the Centre for Green Chemistry and Catalysis (CGCC), the National Research Council (NRC) of Canada – Ocean program and McGill University including the Heather Munroe-Blum Fellowships in Green Chemistry for their financial support.

References

- R. N. Tharanathan and F. S. Kittur, *Crit. Rev. Food Sci. Nutr.*, 2003, **43**, 61–87.
- G. A. Martău, M. Mihai and D. C. Vodnar, *Polymers*, 2019, **11**, 1837.
- M. C. Biswas, B. Jony, P. K. Nandy, R. A. Chowdhury, S. Halder, D. Kumar, S. Ramakrishna, M. Hassan, M. A. Ahsan, M. E. Hoque and M. A. Imam, *J. Polym. Environ.*, 2022, **30**, 51–74.
- F. M. Kerton, Y. Liu, K. W. Omari and K. Hawboldt, *Green Chem.*, 2013, **15**, 860–871.
- R. C. Goy, D. D. Britto and O. B. Assis, *Polimeros*, 2009, **19**, 241–247.
- L.-Y. Zheng and J.-F. Zhu, *Carbohydr. Polym.*, 2003, **54**, 527–530.
- V. K. Mourya and N. N. Inamdar, *React. Funct. Polym.*, 2008, **68**, 1013–1051.
- I. F. Amaral, P. L. Granja and M. A. Barbosa, *J. Biomater. Sci., Polym. Ed.*, 2005, **16**, 1575–1593.
- N. M. Alves and J. F. Mano, *Int. J. Biol. Macromol.*, 2008, **43**, 401–414.
- C. A. G. N. Montalbetti and V. Falque, *Tetrahedron*, 2005, **61**, 10827–10852.
- S. Mondal and S. Malakar, *Tetrahedron*, 2020, **76**, 131662.

- 12 E. A. Werner, *J. Chem. Soc., Trans.*, 1918, **113**, 899–902.
- 13 M. A. Sprung, *Chem. Rev.*, 1940, **26**, 297–338.
- 14 O. I. Afanasyev, E. Kuchuk, D. L. Usanov and D. Chusov, *Chem. Rev.*, 2019, **119**, 11857–11911.
- 15 C. K. S. Pillai, W. Paul and C. P. Sharma, *Prog. Polym. Sci.*, 2009, **34**, 641–678.
- 16 V. Zargar, M. Asghari and A. Dashti, *ChemBioEng Rev.*, 2015, **2**, 204–226.
- 17 A. V. Il'ina and V. P. Varlamov, *Appl. Biochem. Microbiol.*, 2004, **40**, 300–303.
- 18 N. D. Aljbour, M. D. H. Beg and J. Gimbut, *Chem. Eng. Technol.*, 2019, **42**, 1741–1746.
- 19 D. P. Chattopadhyay and M. S. Inamdar, *Int. J. Polym. Sci.*, 2010, **2010**, 939536.
- 20 J. K. Hwang and H. H. Shin, *Korea-Aust. Rheol. J.*, 2000, **12**, 175–179.
- 21 X. Meng and K. J. Edgar, *Prog. Polym. Sci.*, 2016, **53**, 52–85.
- 22 K. Kurita, *Prog. Polym. Sci.*, 2001, **26**, 1921–1971.
- 23 G. M. Gübitz and A. C. Paulo, *Curr. Opin. Biotechnol.*, 2003, **14**, 577–582.
- 24 S. Bhatia, in *Natural Polymer Drug Delivery Systems: Nanoparticles, Plants, and Algae*, Springer International Publishing, Cham, 2016, pp. 95–118, DOI: [10.1007/978-3-319-41129-3_3](https://doi.org/10.1007/978-3-319-41129-3_3).
- 25 P. Ramesh and S. Vinodh, *Int. J. Sustainable Eng.*, 2020, **13**, 411–422.
- 26 L. Shen and M. K. Patel, *J. Polym. Environ.*, 2008, **16**, 154–167.
- 27 S. L. James and T. Friščić, *Chem. Soc. Rev.*, 2013, **42**, 7494–7496.
- 28 L. Takacs, *Chem. Soc. Rev.*, 2013, **42**, 7649–7659.
- 29 J.-L. Do and T. Friščić, *ACS Cent. Sci.*, 2017, **3**, 13–19.
- 30 K. J. Ardila-Fierro and J. G. Hernández, *ChemSusChem*, 2021, **14**, 2145–2162.
- 31 S. Lamour, S. Pallmann, M. Haas and O. Trapp, *Life*, 2019, **9**, 52.
- 32 S. L. James, C. J. Adams, C. Bolm, D. Braga, P. Collier, T. Friščić, F. Grepioni, K. D. Harris, G. Hyett and W. Jones, *Chem. Soc. Rev.*, 2012, **41**, 413–447.
- 33 M. J. Cliffe, C. Mottillo, R. S. Stein, D.-K. Bučar and T. Friščić, *Chem. Sci.*, 2012, **3**, 2495–2500.
- 34 F. Hajiali, T. Jin, G. Yang, M. Santos, E. Lam and A. Moores, *ChemSusChem*, 2022, **15**, e202102535.
- 35 F. Hajiali, J. Vidal, T. Jin, L. C. de la Garza, M. Santos, G. Yang and A. Moores, *ACS Sustainable Chem. Eng.*, 2022, **10**, 11348–11357.
- 36 G. Margoutidis and F. M. Kerton, in *Biomass Valorization*, 2021, pp. 343–365, DOI: [10.1002/9783527825028.ch12](https://doi.org/10.1002/9783527825028.ch12).
- 37 T. Jin, T. Liu, F. Hajiali, M. Santos, Y. Liu, D. Kurdyla, S. Régnier, S. Hrapovic, E. Lam and A. Moores, *Angew. Chem., Int. Ed.*, 2022, **61**, e202207206.
- 38 T. Di Nardo, C. Hadad, A. Nguyen Van Nhien and A. Moores, *Green Chem.*, 2019, **21**, 3276–3285.
- 39 G. Yang, E. Lam and A. Moores, *ACS Sustainable Chem. Eng.*, 2023, **11**, 7765–7774.
- 40 C. Van Poucke, A. Vandeputte, S. Mangelinckx and C. V. Stevens, *Green Chem.*, 2023, **25**, 4271–4281.
- 41 R. Antony, T. Arun and S. T. D. Manickam, *Int. J. Biol. Macromol.*, 2019, **129**, 615–633.
- 42 N. Nigam, S. Kumar, P. Dutta, S. Pei and T. Ghosh, *RSC Adv.*, 2016, **6**, 5575–5581.
- 43 F. Chen, Z. Shi, K. Neoh and E. Kang, *Biotechnol. Bioeng.*, 2009, **104**, 30–39.
- 44 Y. Qin, J. Chen, Y. Bi, X. Xu, H. Zhou, J. Gao, Y. Hu, Y. Zhao and Z. Chai, *Acta Biomater.*, 2015, **17**, 201–209.
- 45 Z. Wei, D. M. Lewis, Y. Xu and S. Gerecht, *Adv. Healthcare Mater.*, 2017, **6**, 1700523.
- 46 B. C. E. Makhubela, A. Jardine and G. S. Smith, *Appl. Catal., A*, 2011, **393**, 231–241.
- 47 R. Antony, S. T. David, K. Karuppasamy, G. Sanjeev and S. Balakumar, *Spectrochim. Acta, Part A*, 2014, **124**, 178–186.
- 48 S. W. Gong, H. F. He, C. Q. Zhao, L. J. Liu and Q. X. Cui, *Synth. Commun.*, 2012, **42**, 574–581.
- 49 D. H. K. Reddy and S.-M. Lee, *J. Appl. Polym. Sci.*, 2013, **130**, 4542–4550.
- 50 H. Xiao, W. Lu, X. Le, C. Ma, Z. Li, J. Zheng, J. Zhang, Y. Huang and T. Chen, *Chem. Commun.*, 2016, **52**, 13292–13295.
- 51 S. Prasad, T. Gomathi and P. Sudha, *Int. J. Novel Trends Pharm. Sci.*, 2017, **7**, 57–63.
- 52 E. L. de Araújo, H. F. G. Barbosa, E. R. Dockal and É. T. G. Cavalheiro, *Int. J. Biol. Macromol.*, 2017, **95**, 168–176.
- 53 H. R. Mardani, F. Ravari, A. Kalaki and L. Hokmabadi, *J. Polym. Environ.*, 2020, **28**, 2523–2538.
- 54 N. Krrushcheva, N. Loim and V. Sokolov, *Russ. Chem. Bull.*, 1997, **46**, 1952–1955.
- 55 D. E. Crawford, C. K. G. Miskimmin, A. B. Albadarin, G. Walker and S. L. James, *Green Chem.*, 2017, **19**, 1507–1518.
- 56 F. A. W. Fatika, M. Anwar, D. J. Prasetyo, W. A. Rizal, R. Suryani, P. Yuliyanto, S. Hariyadi, A. Suwanto, N. A. Bahmid, S. K. Wahono, F. H. Sriherfyna, C. D. Poeloengasih, B. Purwono, E. Agustian, R. Maryana and H. Hernawan, *Int. J. Biol. Macromol.*, 2023, **247**, 125759.
- 57 E. H. Cordes and W. P. Jencks, *J. Am. Chem. Soc.*, 1962, **84**, 832–837.
- 58 E. H. Cordes and W. P. Jencks, *J. Am. Chem. Soc.*, 1963, **85**, 2843–2848.
- 59 P. S. Reddy, S. Kanjilal, S. Sunitha and R. B. N. Prasad, *Tetrahedron Lett.*, 2007, **48**, 8807–8810.
- 60 G. Borg, D. A. Cogan and J. A. Ellman, *Tetrahedron Lett.*, 1999, **40**, 6709–6712.
- 61 A. Heydari, A. Arefi and M. Esfandyari, *J. Mol. Catal. A: Chem.*, 2007, **274**, 169–172.
- 62 K. N. Gusak, Z. V. Ignatovich and E. V. Koroleva, *Russ. Chem. Rev.*, 2015, **84**, 288.
- 63 M. A. Ayedi, Y. Le Bigot, H. Ammar, S. Abid, R. E. Gharbi and M. Delmas, *Synth. Commun.*, 2013, **43**, 2127–2133.
- 64 U. Janciauskaite, V. Rakutyte, J. Miskinis and R. Makuska, *React. Funct. Polym.*, 2008, **68**, 787–796.

- 65 H. E. Abdelwahab, S. Y. Hassan, G. A. Yacout, M. A. Mostafa and M. M. El Sadek, *Polymers*, 2015, **7**, 2690–2700.
- 66 W. Yao, Y. Jiao, J. Luo, M. Du and L. Zong, *Int. J. Biol. Macromol.*, 2012, **50**, 821–825.
- 67 E. I. Rabea, M. E. Badawy, T. M. Rogge, C. V. Stevens, M. Höfte, W. Steurbaut and G. Smaghe, *Pest Manage. Sci.*, 2005, **61**, 951–960.
- 68 E. Bobu, R. Nicu, M. Lupei, F. Ciolacu and J. Desbrieres, *Cellul. Chem. Technol.*, 2011, **45**, 619.
- 69 T. Frišćić, S. L. Childs, S. A. A. Rizvi and W. Jones, *CrystEngComm*, 2009, **11**, 418–426.
- 70 J. Mack, D. Fulmer, S. Stofel and N. Santos, *Green Chem.*, 2007, **9**, 1041–1043.
- 71 S. Perrone, A. Salomone, A. Caroli, A. Falcicchio, C. Citti, G. Cannazza and L. Troisi, *Eur. J. Org. Chem.*, 2014, 5932–5938.
- 72 S. D. Montag, *J. Chem. Educ.*, 2023, **100**, 4456–4461.
- 73 Z.-W. Jing, Z.-W. Ma, C. Li, Y.-Y. Jia, M. Luo, X.-X. Ma, S.-Y. Zhou and B.-L. Zhang, *Bioorg. Med. Chem. Lett.*, 2017, **27**, 1003–1006.
- 74 H. C. B. Paula, R. B. C. Silva, C. M. Santos, F. D. S. Dantas, R. C. M. de Paula, L. R. M. de Lima, E. F. de Oliveira, E. A. T. Figueiredo and F. G. B. Dias, *Int. J. Biol. Macromol.*, 2020, **163**, 1591–1598.