

# Journal of Materials Chemistry A

Materials for energy and sustainability

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: S. Sun, J. Zhou, S. Xi, H. R. Tan, F. Wei, H. L. Seng, W. Y. Lieu, Y. Ren, S. Wang and Z. W. Seh, *J. Mater. Chem. A*, 2024, DOI: 10.1039/D4TA02175D.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

# Short-range disorder mediated stability of Zn in rock-salt MgO beyond configurational entropy

View Article Online

DOI: 10.1039/B4TA02175D

Shengnan Sun<sup>1,†,\*</sup>, Jun Zhou<sup>1,†</sup>, Shibo Xi<sup>2,†</sup>, Hui Ru Tan<sup>1</sup>, Fengxia Wei<sup>1</sup>, Debbie Hwee Leng Seng<sup>1</sup>, Wei Ying Lieu<sup>1,3</sup>, Yi Ren<sup>1</sup>, Shijie Wang<sup>1,\*</sup> and Zhi Wei Seh<sup>1,\*</sup>

<sup>1</sup> Institute of Materials Research and Engineering (IMRE), Agency for Science, Technology and Research (A\*STAR), 2 Fusionopolis Way, Innovis #08-03, Singapore 138634, Republic of Singapore

<sup>2</sup> Institute of Sustainability for Chemicals, Energy and Environment (ISCE<sup>2</sup>), Agency for Science, Technology and Research (A\*STAR), 1 Pesek Road, Jurong Island, Singapore 627833, Republic of Singapore

<sup>3</sup> Pillar of Engineering Product Development, Singapore University of Technology and Design, 8 Somapah Road, Singapore 487372, Republic of Singapore

† S.S., J.Z. and S.X. contributed equally to this work.

\*Corresponding author. E-mail: sun\_shengnan@imre.a-star.edu.sg; sj-wang@imre.a-star.edu.sg; sehzw@imre.a-star.edu.sg



## Abstract

View Article Online  
DOI: 10.1039/D4TA02175D

High-entropy rock-salt  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$  has been intensively studied in the energy field due to its unique composition-function relationship and synergistic effect. Entropy-stabilization of Cu and Zn in rock-salt  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$  is the key characteristic of this material. As a parent binary oxide, ZnO exists as wurtzite in nature. Herein, for the first time we investigated the role of late 3d transition metals Co, Ni and Cu in stabilizing Zn in MgO-based rock-salt oxides under the same configurational entropy condition and their structure stability in alkaline solution. We found that Co, Ni and Cu can increase the Zn solubility in MgO-based rock-salt oxides,  $\text{Mg}_{0.50}\text{TM}_{0.25}\text{Zn}_{0.25}\text{O}$  (TM = Co, Ni and Cu, configurational entropy 1.04 R), with Cu being the best. Simulation results show that the formation energy of Zn substitution for Mg is the lowest in  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ . Moreover, Cu incorporation can create a wide metal-oxygen bond length distribution, which causes short-range disorder and enhances Zn stabilization. Surprisingly, CuO with square-planar Cu-O coordination is more effective in stabilizing rock-salt ZnO in MgO, compared to rock-salt CoO and NiO, as  $\text{Cu}^{2+}$  ions undergo splitting of  $e_g$  orbitals due to strong Jahn-Teller distortion.  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  with medium entropy 1.04 R can stabilize 25 at% Cu and 25 at% Zn simultaneously. Besides, the Ni substitution is found to be effective in improving the structure stability in alkaline solution. This work gives insight in understanding the complementation of orbital distribution in high-entropy oxides for metal stabilization, and provides a rational composition design for applications in the energy field.



## 1. Introduction

High-entropy oxides (HEOs) are single-phase oxide solid solutions that have a configurational entropy greater than  $1.5R$  and contain five or more cations<sup>1, 2</sup> Recently, HEOs with various crystal structures have demonstrated great potential and enhanced properties in the energy field,<sup>3-5</sup> such as in electrocatalysis and battery areas, due to the synergistic effect and unique composition-function relationship.<sup>6, 7</sup> For example, enhanced oxygen evolution reaction (OER) on perovskite HEO  $\text{LaCr}_{0.2}\text{Mn}_{0.2}\text{Fe}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{O}_{3-\delta}$  has been reported compared with all its parent compounds  $\text{LaMO}_3$  ( $M = \text{Cr, Mn, Fe, Co, Ni}$ ), which is ascribed to a synergistic effect in the adsorbate binding on several transition metal surfaces.<sup>8</sup> The HEO composition for better OER is also optimized by Nguyen et al. to  $\text{La}(\text{CrMnFeCo}_2\text{Ni})\text{O}_3$ .<sup>9</sup> Enhanced OER is also observed on the spinel HEO  $(\text{Fe}_{0.20}\text{Co}_{0.20}\text{Ni}_{0.20}\text{Cu}_{0.20}\text{Zn}_{0.20})\text{Al}_2\text{O}_4$  by Katzbaer et al., which is attributed to a narrower band gap of the HEO than that of all parent spinel oxides.<sup>10</sup> We recently also found surface entropy evolution on spinel HEO  $\text{Zn}(\text{CrMnFeCoNi})_2\text{O}_4$  during OER cycling, accompanied with the changed reaction mechanism and promoted OER performance.<sup>11</sup> In the battery area, Liu et al. investigated the Co concentration effect in spinel  $(\text{CrFeMnNiCo}_x)_3\text{O}_4$  on Li storage and found that higher Co concentrations contribute to higher Li storage capability.<sup>12</sup>


Besides perovskite and spinel HEOs, the rock-salt HEOs also exhibit excellent performance in catalysis<sup>13</sup>, anode<sup>14, 15</sup> and cathode<sup>16</sup> in batteries, in particular,  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$ , as a single phase stabilizing tenorite CuO and wurtzite ZnO in a single rock-salt structure by configurational entropy.<sup>2</sup> In the study by Liu et al.,  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$  has regulated electronic and geometric structures for superior intrinsic OER activity compared with CoO, NiO, and  $\text{Co}_{0.5}\text{Ni}_{0.5}\text{O}$ .<sup>17</sup> In our recent study, we found that the ammonia generation from nitrate reduction can be promoted on  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$  due to spin-related Cu-Co pair.<sup>13</sup> In battery anodes, the cycling performance of  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$  and the synergy of cations have been intensively investigated. Sarkar et al. reported that entropy-stabilization in  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$  is beneficial to the Li-ion anode cycling stability, and the removal any one of Co, Cu and Zn underwent severe capacity degradation, especially Co.<sup>14</sup> Inactive material MgO and well-mixed cations in HEO is found to be essential to remarkable cycling, rate performance and high capacity by Qiu et al.<sup>18</sup> The lithiation-delithiation process of  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$  was investigated by Ghigna et al. using X-ray absorption spectroscopy (XAS) and indicated that the reduction of cations begins from Cu to Co and Ni, followed by alloying Mg and Zn with Li, and furthermore the reaction is not fully reversible. They also suggest that both ZnO and MgO, especially MgO, are responsible for the capacity compared with the oxides without Mg and Zn.



<sup>19</sup> Moreover, in the XAS study by Wang et al., metallic Co, Ni, Cu and Zn were observed and rock-salt fcc Mg-dominated oxide matrix was left after lithiation, while Cu, Ni and a large fraction of Co were not being oxidized after delithiation.<sup>20</sup> Additionally, an improvement in Li-storage was reported in Li-substituted (MgCoNiZn)O<sup>21</sup> and (MgCoNiCuZn)O<sup>22</sup>, which are ascribed to the generation of oxygen vacancy. These findings imply the significance of the intrinsic composition-function relationship in cubic rock-salt oxides in electrocatalysis and Li-ion batteries.

While Mg<sub>0.2</sub>Co<sub>0.2</sub>Ni<sub>0.2</sub>Cu<sub>0.2</sub>Zn<sub>0.2</sub>O is considered as an entropy-stabilized oxide that stabilizes tenorite CuO and wurtzite ZnO in a single rock-salt structure, an investigation by Fracchia et al. demonstrates an important role of solubility in stabilizing Cu<sup>2+</sup> ( $t_{2g}^6e_g^3$  in 3d orbitals) in rock-salt oxides beyond configurational entropy.<sup>23</sup> Aamlid et al. categorized HEOs from two characteristics, configurational entropy and entropy stabilization, that is, conventional solid solutions have low configurational entropy and are not entropy-stabilized while HEOs exhibit either configurational entropy ( $> 1.5R$ ) and / or entropy stabilization.<sup>24</sup> Brahlek et al. indicated that “entropy-stabilized” as a subset of “high-entropy” does not necessarily restrict the equilibrium entropy stabilization at room temperature.<sup>25</sup> Chen et al. experimentally pointed out the formation of entropy-stabilized oxide does not necessarily need the configurational entropy to reach 1.5R and the critical temperature is significant in annealing process for obtaining a single-phase state, taking medium configurational entropy (Mg<sub>1/3</sub>Co<sub>1/3</sub>Ni<sub>1/3</sub>)<sub>1-x</sub>Zn<sub>x</sub>O for example.<sup>26</sup> Besides CuO, ZnO is also stabilized in the cubic rock-salt phase Mg<sub>0.2</sub>Co<sub>0.2</sub>Ni<sub>0.2</sub>Cu<sub>0.2</sub>Zn<sub>0.2</sub>O. Differing from Cu<sup>2+</sup>, Zn<sup>2+</sup> has fully occupied 3d orbitals that are symmetrical in all directions with an electron configuration of [Ar]3d<sup>10</sup>. Wurtzite ZnO has a typical sp<sup>3</sup> covalent bonding and a substantial ionic character.<sup>27</sup> ZnO is identified as a selective electrocatalyst for water oxidation (to generate hydrogen peroxide<sup>28</sup> and oxygen<sup>29</sup>), oxygen reduction reaction<sup>30</sup>, CO<sub>2</sub> reduction<sup>31, 32</sup>, as well as a suitable coating material for carbon anode<sup>33</sup> and LiCoO<sub>2</sub> cathode<sup>34</sup> in Li-ion batteries.

Inspired by the phase stabilization works above and the composition-function relationship in electrocatalysis and batteries, herein for the first time, we unveil the Zn stabilization in the MgO-based rock-salt Mg<sub>0.75-x</sub>TM<sub>x</sub>Zn<sub>0.25</sub>O (TM = Co, Ni and Cu) in powder form by focusing on the impact of late 3d transition metals Co, Ni and Cu. We chose MgO as the matrix due to the stable orbital 1s<sup>2</sup>2s<sup>2</sup>2p<sup>6</sup>, non-magnetic properties of Mg<sup>2+</sup> ions and wide application in the energy fields, for example, as promoter in oxygen electrochemistry<sup>35, 36</sup> and alcohol electrooxidation<sup>37, 38</sup>, and as coating to improve the electrode stability and capacity retention in batteries<sup>39-42</sup>. We found that the substitution of Co, Ni and Cu for Mg can increase the Zn




solubility, among which Cu is the most effective, which is contrary to the intuition that CoO and NiO could be more effective because of their rock-salt structure. We also found the Ni substitution is effective to improve the resistance to alkaline solution and structure stability. Our results provide a design guideline for increasing doping amount with the assistance of another transition metal, potentially in tuning Zn fractions and structure stability in solution. We also for the first time indicate that the medium-entropy  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  (1.04 R) suffices for stabilizing 25 at% Cu and 25 at% Zn in the rock-salt structure simultaneously.

## 2. Experimental

### 2.1. Materials

The oxides were synthesized by the sol-gel method as our previous report.<sup>13</sup> All chemicals were purchased from Sigma-Aldrich, including magnesium nitrate hexahydrate, cobalt nitrate hexahydrate, nickel nitrate hexahydrate, copper nitrate hemi(pentahydrate), zinc nitrate hexahydrate, nitric acid and citric acid, and urea. The metal nitrates, citric acid, and urea were dissolved in de-ionized water with the feeding mole ratio of 1 : 2 : 2 with less nitric acid under stirring. The solution was kept at ~95 °C until the gel formed and then dried at 170°C in the oven overnight. This was followed by annealing at 1000 °C for 6 h at a 5°C min<sup>-1</sup> ramping rate and cooling down naturally. The stability of these oxides in alkaline was evaluated by soaking these oxides in 2 M KOH for four weeks at room temperature under constant stirring. The oxides were collected by centrifuge at 8000 rpm and then drying in the oven overnight. The procedure of centrifuge is as follow. First, the alkaline centrifugate was removed by centrifugation. Then, the remaining oxides were washed by centrifugation at least twice in deionised water until the centrifugate was neutral, followed by a single wash in ethanol. X-ray diffraction (XRD, Bruker D8 Advance using Cu-K $\alpha$  radiation) was used to characterize the crystal structure. Rietveld refinement was conducted using TOPAS v5, using fundamental parameters and full axial model. Scanning electron microscope (SEM, JEOL JSM7600F equipped with Oxford Instruments X-Max 50mm<sup>2</sup> detector) and transmission electron microscope (TEM, FEI Titan equipped with EDAX detector) were used to obtain the morphology and energy-dispersive X-ray spectroscopy (EDX) mapping. SEM-EDX was used to obtain the atomic ratios of metal elements by at least three independent measurements. The extended X-ray absorption fine structure (EXAFS) and X-ray absorption near edge structure (XANES) were studied at the Singapore Synchrotron Light Source, XAFCA beamline. The X-ray photoelectron spectroscopy (XPS) was carried out using Thermo Fisher Scientific Theta Probe and the binding energy was calibrated from carbon contamination (C 1 s peak 284.8 eV).



The number of XPS scans was adjusted as needed to achieve a high resolution and signal-to-noise ratio, considering the possibly low ratio of some metal elements. The XPS of commercial MgO (Kanto Chemical), CoO (Alfa Aesar), NiO (Sigma-Aldrich), CuO (Sigma-Aldrich) and ZnO (Kanto Chemical) were used as control and reference.

## 2.2. Calculation

The solid solution of oxides is effectively modeled using special quasirandom structures (SQSs) generated by the Alloy Theoretic Automatic Toolkit (ATAT)<sup>43</sup>. These SQSs are designed to minimize pair correlation differences with the ideally random alloy within a radius greater than 7 Å. The size of the SQSs is consistently set to 64 atoms, corresponding to 2×2×2 supercells of the rock-salt oxides. To perform further density functional theory (DFT) simulations, the generated SQS structures serve as initial configurations and are inputted into the Vienna ab initio Simulation Package (VASP 5.4.4)<sup>44, 45</sup>. The Perdew-Burke-Ernzerhof (PBE) approximation is utilized for the exchange-correlation functional, and the frozen-core all-electron projector augmented wave (PAW) method is employed to describe the electron-ion interaction<sup>46</sup>. The cutoff energy for the plane wave expansion is set to 600 eV. For all simulations, a Monkhorst-pack 6×6×6 k-point grid is applied. Moreover, the generalized gradient approximation (GGA) with Hubbard U is used specifically for the d orbitals of Ni, Cu, and Co<sup>47,48</sup>. The Hubbard U parameters for Ni, Cu, and Co are determined based on suggested values from systematic investigations carried out using high-throughput simulations<sup>49</sup>. While the lattice vectors of the SQS structures are kept fixed, their scale factors are optimized during the simulations. The atoms within the structure are fully relaxed until both the energy and force converge to 10<sup>-5</sup> eV and 0.01 eV/Å, respectively.

## 3. Results & Discussion


### 3.1. Material structure and morphology

Fig. 1a shows the XRD patterns of Mg<sub>0.75</sub>Zn<sub>0.25</sub>O, Mg<sub>0.50</sub>Co<sub>0.25</sub>Zn<sub>0.25</sub>O, Mg<sub>0.50</sub>Ni<sub>0.25</sub>Zn<sub>0.25</sub>O and Mg<sub>0.50</sub>Cu<sub>0.25</sub>Zn<sub>0.25</sub>O, and the Rietveld refinements can be found in Figs. S1-S4. Mg<sub>0.75</sub>Zn<sub>0.25</sub>O has an obvious rock-salt structure (Fm-3m, lattice parameter  $a = 4.2278$  Å) and contains the second phase wurtzite ZnO (1.52 wt%). The diffraction peaks corresponding to the rock-salt structure shift to a lower angle compared to the standard rock-salt MgO, indicating that Zn introduction increases the lattice constant according to Bragg's law. Such an increase in the lattice constant is consistent with the effective ionic radii order: Zn<sup>2+</sup> (0.745 Å) > Mg<sup>2+</sup> (0.720 Å)<sup>50</sup>. When substituting Co, Ni and Cu for Mg, the wurtzite ZnO peaks became weaker and




even disappeared.  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  is a single rock-salt phase (lattice parameter  $a = 4.2428$  Å) without the wurtzite ZnO impurity, which indicates that Co is effective in increasing Zn solubility in rock-salt MgO. However, the diffraction peaks of  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  have lower intensities compared with that of  $\text{Mg}_{0.75}\text{Zn}_{0.25}\text{O}$ , indicating that Co substitution reduces the crystallization. The Ni substitution for Mg only increases Zn solubility and rock-salt structure crystallization (lattice parameter  $a = 4.2200$  Å), however an impurity-free single rock-salt  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  could not be obtained (0.088 wt% ZnO). Apart from Co and Ni substitution, substituting Cu for Mg also increases Zn solubility in rock-salt MgO and makes  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  a single rock-salt phase (lattice parameter  $a = 4.2394$  Å). Different from the XRD profiles of  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$ ,  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  has a strong (111) diffraction peak, indicating Cu can increase the order in the [111] direction. It is well known that the (111) planes in rock-salt oxides consist of either metal atoms or oxygen atoms exclusively, and metal atoms contribute more than oxygen atoms in the diffraction peak intensity due to their relatively higher masses.  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  has a low intensity ratio of  $I(200)/I(111)$ , indicative of the less ordered (200) planes, which can be explained using Jahn-Teller effect induced by  $\text{Cu}^{2+}$ .<sup>51</sup> To further compare the enhancement effect between Co and Cu on Zn solubility, we increased the Zn fraction to 30 at% and found that Cu is more effective than Co (Fig. S5).

The SEM images show that  $\text{Mg}_{0.50}\text{TM}_{0.25}\text{Zn}_{0.25}\text{O}$  (TM = Co, Ni and Cu) exist in the form of particles without regular morphology (Fig. 1b and Fig. S6). The particles have good crystallization. For example, the TEM images show the (111), (200) and (220) lattices of  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ , corresponding to 0.243 nm, 0.210 nm and 0.151 nm, respectively, consistent with the XRD pattern (Fig. 1c and Fig. S7). The selected area electron diffraction (SAED) pattern (Fig. 1d) shows that the particle exists in the form of single crystal, corresponding to the location in Fig. 1c. The SEM-EDX mapping results indicate that the element distribution is homogeneous in these three oxides (Fig. S8). Furthermore, the metal element ratios in the oxides are close to the metal precursor feeding ratios (Table S3-S5). Within a single particle, the element distribution is also homogeneous as evidenced by the TEM-EDX mapping of Mg, Cu, Zn and O in Fig. 1e.






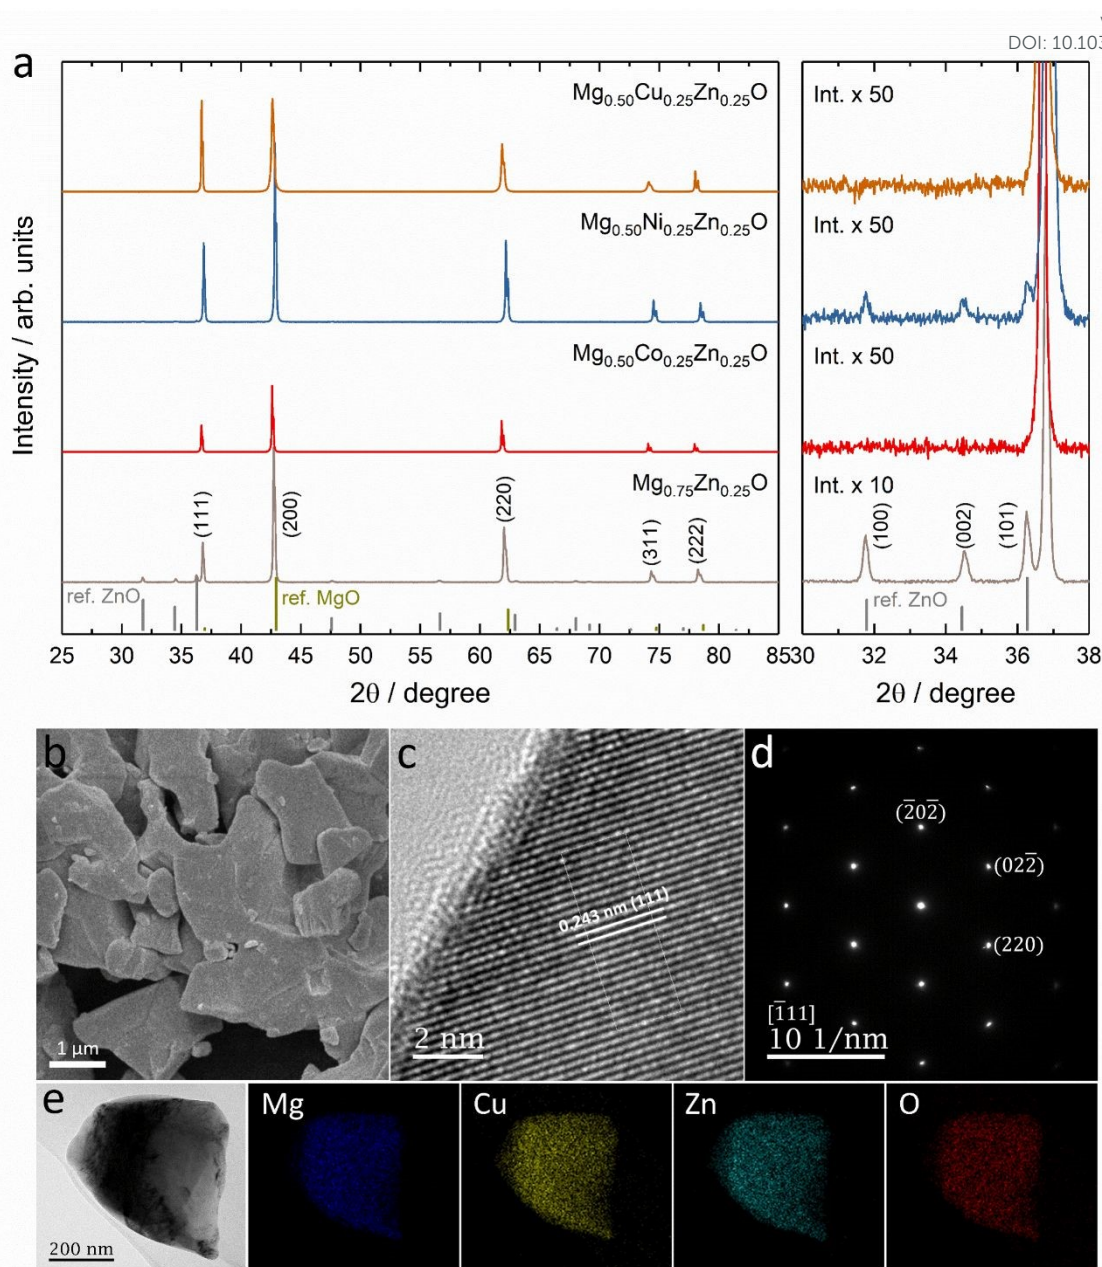


**Fig. 1.** (a) XRD patterns of Co, Ni and Cu substituted  $\text{Mg}_{0.75}\text{Zn}_{0.25}\text{O}$ . XRD standard peak: MgO refers to PDF 00-045-0946 and ZnO refers to PDF 00-036-1451. (b) SEM image, (c) HRTEM image, (d) SAED pattern at the location in (c), and (e) TEM-mapping of  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ .

Fig. 2 shows the  $k^3$ -weighting Fourier-transformed EXAFS (FT-EXAFS) results of Zn, Co, Ni and Cu in  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ ,  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ . The experimental EXAFS data can be found in Figs. S9-S10. In Fig. 2a, the peaks at around 1.66-1.69 Å and at 2.58 Å are attributed to the first-shell neighbour (Zn-O) and the second-shell neighbour Zn-metal scattering, respectively. Similar attributions can be made to Co/Ni/Zn for the peaks in Fig. 2b.<sup>52</sup> Considering the peak position at distances in FT-EXAFS is shifted from the




real interatomic distance by 0.2-0.5 Å,<sup>53</sup> the EXAFS fitting is performed to obtain the nearest metal-oxygen and metal-metal distances as well as the coordination number. The fitted results for the first and second shells and the parameters can be found in Fig. 2, Fig. S11, Table 1 and Table S1. Theoretically, in ideal cubic rock-salt oxides the first-shell coordination number of metal with oxygen is 6 and the second-shell coordination number of metal with metal is 12. From Table 1, in  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$ , the first-shell distances of Zn-O, Co-O, and Ni-O are close ( $\sim 2.12$  Å). The first-shell coordination number of Zn with O is around 5.7, which is lower than that of Co/Ni (around 6.3). The first-shell Zn-O distance and the coordination number of Zn in  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  are close to that in  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$ , while the Cu-O distance (2.00 Å) and coordination number (3.1) are much smaller compared with Zn, Co and Ni. It could be caused by the Jahn-Teller distortion of  $\text{Cu}^{2+}$  ions.<sup>51</sup> In  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ , the second-shell Zn-Mg/Cu/Zn distances are in the range of 2.98 to 3.00 Å. The coordination number of Zn with Mg is 7.9, which is larger than 6 (based on the metal stoichiometric ratio in the oxides), while the coordination number of Zn with Cu/Zn is 2.1, smaller than 6. It suggests that more Mg instead of Cu/Zn occupy the second shell of Zn. Cu has a normal coordination number of 6.1 with Mg and a smaller one of 1.2 with Cu/Zn, which means Cu has a low coordination environment in the second shells, suggesting the less ordered structure around Cu. In  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$ , the same Zn-Mg and Ni-Mg distance 2.96 Å is calculated in the second shell of Zn and Ni with the coordination number 7.9 and 8.1, respectively. Zn-Ni/Zn and Ni-Ni/Zn have the close distances 2.98 Å and 2.97 Å, and coordination number 2.0 and 2.3 with Ni/Zn, respectively. Compared with  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ , Zn in  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  has a close coordination number (8.1) with Mg and a much smaller coordination number (0.2) with Co/Zn, suggesting Zn is less coordinated in the second shell, particularly with Co/Zn. In contrast with Zn, Co has a larger coordination number of 9.6 with Mg and 2.8 with Co/Zn. It indicates that more metals are around Co and less around Zn. Besides, Zn-Mg, Zn-Co/Zn, Co-Mg and Co-Co/Zn in  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  have a very close distance around 2.98 Å.

Considering the deviation of coordination number from ideal values, additional fitting has been performed by fixing the coordination numbers. For Co, Ni and Zn, the first-shell coordination number of the metal with oxygen is fixed to 6, while for Cu, 4 planar and 2 axial coordinating oxygens are considered<sup>54</sup>. Because the coordinating metals are randomly distributed and cannot be identified precisely<sup>55</sup>, the total second-shell coordination number of metal with metal is fixed to 12. The fitted results and the parameters applied can be found in Figs. S12-S13, Table 2 and Table S2. The fitted Zn-O distances are about 2.14 Å in



$\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ ,  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ , which are very close to the fitted values in Table 1. The Co-O and Ni-O distances remain unchanged for the two fittings. For Cu-O, the planar distance is 2.02 Å and the axial distance is 2.28 Å, which are close to reported values in  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$ <sup>54-56</sup>. For  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$ , the fitted second-shell metal-metal distances do not change significantly before and after fixing the coordination numbers. In  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ , the fitted Cu-Mg and Cu-Cu/Zn distances are the same with the values in Table 1, while a dramatic metal-metal distance decrease is observed in Zn-Mg and Zn-Cu/Zn. Though the second-shell coordination numbers for the specific metals still deviate from the ideal coordination numbers after fixing the total coordination number, the trend remains similar to that shown in Table 1.

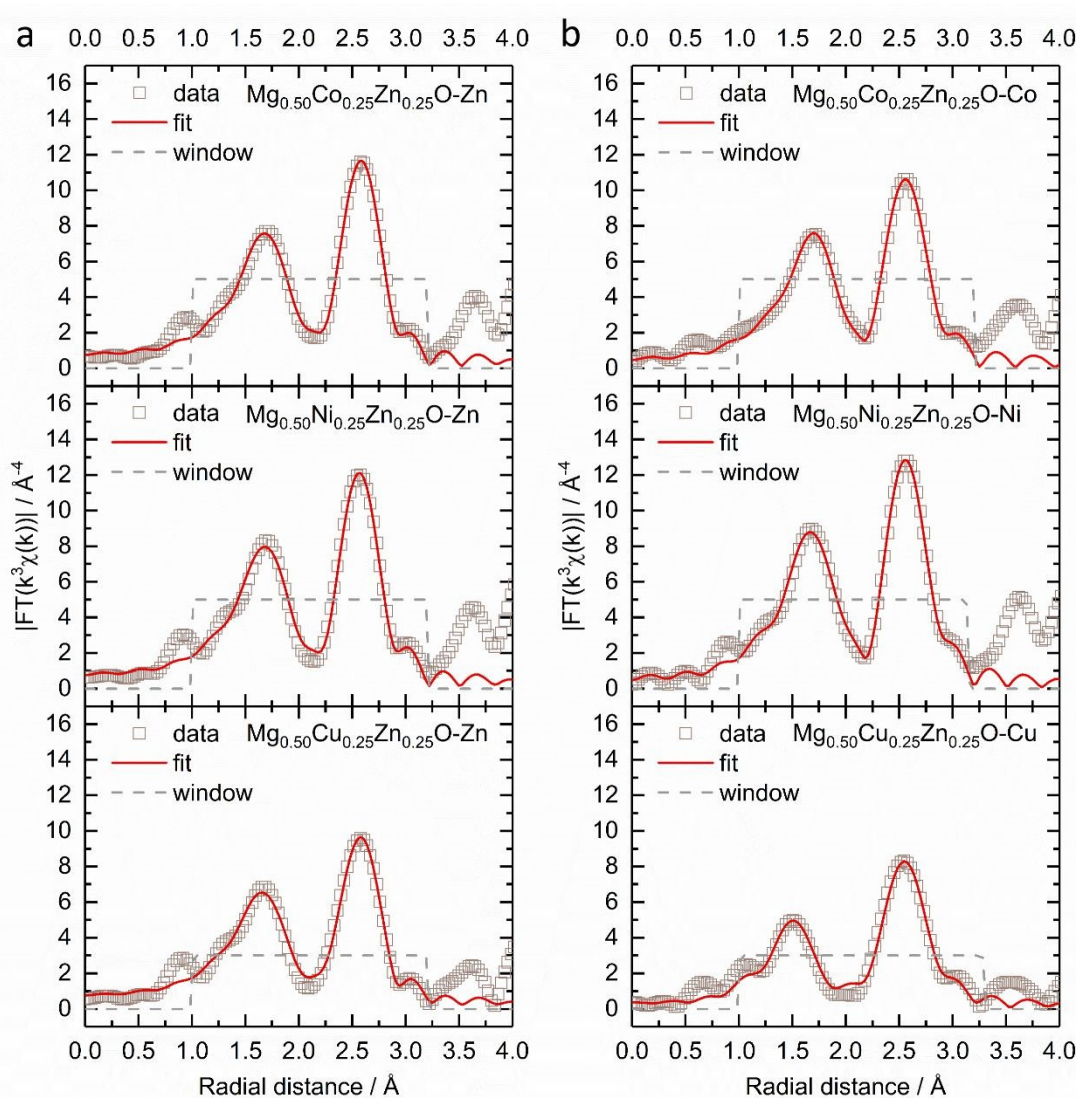

**Fig. 2.** The  $k^3$ -weighting FT-EXAFS and the fitting of (a) Zn K-edge and (b) Co, Ni and Cu K-edges of  $\text{Mg}_{0.50}\text{TM}_{0.25}\text{Zn}_{0.25}\text{O}$  (TM = Co, Ni, Cu) under a Hanning-shaped window.



**Table 1.** EXAFS fitting results for interatomic distances and coordination numbers. For each element pair, the number before the slash is the distance between them, and the one after the slash is the coordination number of the first element with the second element.


	Zn-O	TM-O	Zn-Mg	Zn-TM/Zn	TM-Mg	TM-TM/Zn
$\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$	2.13 Å /5.6	2.12 Å /6.4	2.99 Å /8.1	2.99 Å /0.2	2.98 Å /9.6	2.98 Å /2.8
$\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$	2.12 Å /5.7	2.10 Å /6.2	2.96 Å /7.9	2.98 Å /2.0	2.96 Å /8.1	2.97 Å /2.3
$\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$	2.12 Å /5.7	2.00 Å /3.1	2.98 Å /7.9	3.00 Å /2.1	2.97 Å /6.1	2.99 Å /1.2

**Table 2.** EXAFS fitting results for interatomic distances and coordination numbers, fixing the coordination number to 6 for the first shell and 12 for the second shell. For each element pair, the number before the slash is the distance between them, and the one after the slash is the coordination number of the first element with the second element.

	Zn-O	TM-O	Zn-Mg	Zn-TM/Zn	TM-Mg	TM-TM/Zn
$\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$	2.14 Å /6	2.12 Å /6	3.02 Å /11.5	3.01 Å /0.5	2.98 Å /9.4	2.98 Å /2.6
$\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$	2.13 Å /6	2.10 Å /6	2.97 Å /9.0	2.97 Å /3.0	2.97 Å /8.9	2.97 Å /3.1
$\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$	2.14 Å /6	2.02 Å /4 2.28 Å /2	2.88 Å /9.7	2.75 Å /2.3	2.97 Å /8.7	2.99 Å /3.3

### 3.2. Electronic states


The electronic states of Co, Ni, Cu and Zn were further investigated by XANES (Fig. S14). No obvious change can be observed in the Zn K-edge XANES profile amongst  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ ,  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  (Fig. S14a), while their Zn profiles differ from those of ZnO and the reported profile.<sup>57</sup> In ZnO (Fig. S14a), one small shoulder E1 at ~9663.5 eV, peaks E2 at ~9669.3 eV and E3 at ~9680.3 eV, and EXAFS oscillation E4 at ~9714.9 eV are observed, consistent with the reported ZnO profile by Rodrigues et al.<sup>57</sup> Moreover, the E3 peaks for Zn in  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ ,  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  are shifted by ~ 5 eV to higher energy with respect to ZnO, which are also consistent with the report on wurtzite ZnO and cubic ZnO<sup>58</sup>. This can be explained by the difference in Zn chemical environment in these three oxides and wurtzite ZnO. This is in contrast with the Co and Ni XANES profiles of  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$ , which have no obvious changes and energy shifts compared to commercial CoO and NiO (Fig. S14b and S14c), thus suggesting that the Co and Ni valence states are close to +2. Fig. S14d shows that the Cu XANES profile is different from that of commercial CuO, which can be explained that the environment of Cu in  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  is different from that in tenorite CuO. Besides XANES, XPS are used to further reveal the surface electronic state of  $\text{Mg}_{0.50}\text{TM}_{0.25}\text{Zn}_{0.25}\text{O}$  (TM = Co, Ni, Cu) (Fig. 3 and Fig. S15). The XPS results of commercial MgO, CoO, NiO, CuO and



ZnO are also provided in Figs. S16-S17 as references. The Zn 2p profiles have no obvious change among  $\text{Mg}_{0.50}\text{TM}_{0.25}\text{Zn}_{0.25}\text{O}$  (TM = Co, Ni, Cu) (Figs. 3a, c, e), and the binding energies of Zn 2p<sub>3/2</sub> (~1021.3 eV) and Zn 2p<sub>1/2</sub> (~1044.4 eV) and their difference (~23.1 eV) are almost the same with that of the commercial ZnO (Fig. S16c). This indicates a valence state of +2 for Zn. The Co 2p<sub>3/2</sub> spectrum in  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  is split into three peaks at 779.8 eV, 781.5 eV and 786.5 eV, respectively (Fig. 3b), which have the similar profile with that of the commercial CoO (Fig. S17a) and the report by Biesinger et al.<sup>59</sup> The binding energies of 779.8 eV and 786.5 eV can be assigned to Co<sup>2+</sup> and the satellite, respectively. The attribution to the binding energy of 781.2 eV is still under debate. Some works assigned it to Co<sup>2+</sup>,<sup>60, 61</sup> while others to Co<sup>3+</sup>.<sup>59, 62</sup> The early work by McIntyre and Cook indicated that the Co formal oxidation states are hardly differentiated from the binding energy.<sup>63</sup> The Ni 2p<sub>3/2</sub> profile has a main peak at 854.9 eV and a satellite peak at 860.8 eV (Fig. 3d), which agrees with our reported one in  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$ . The main peak has no obvious doublet structure at 853.5 eV (local screening) and 855.4 eV (nonlocal screening)<sup>52, 64</sup> like commercial NiO (Fig. S17c). The missing peak can be explained by negligible nonlocal screening contribution from Ni as next nearest neighbours as the diluted NiO in MgO-ZnO matrix,<sup>65</sup> which is in agreement with the report by Altieri et al.<sup>66</sup> The attribution of Cu 2p<sub>3/2</sub> profile in Fig. 3f is similar to our previous report<sup>13</sup> and commercial CuO in Fig. S17e. The main difference is the relative intensity of Cu<sup>+</sup> (932.5 eV) on the surface. Besides, no obvious changes of Mg 1s profiles are observed in  $\text{Mg}_{0.50}\text{TM}_{0.25}\text{Zn}_{0.25}\text{O}$  (TM = Co, Ni, Cu) (Fig. S15) and commercial MgO (Fig. S16), indicating the existence of Mg<sup>2+</sup> in the oxides. The O 1s has three distinct peaks at 529.3 eV, 531.0 eV and 533.0 eV (Fig. S15), take the O 1s profile of  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  as example, which are assigned to lattice oxygen, oxygen vacancy and chemically adsorbed oxygen, respectively.<sup>21, 67</sup> The recent work by Frankcombe and Liu<sup>68</sup> pointed out that the binding energy of 531 eV is ascribed to the water molecules strongly bound to the surface as distinct from more loosely bound water at 533 eV.

View Article Online  
DOI: 10.1039/D4TA02175D



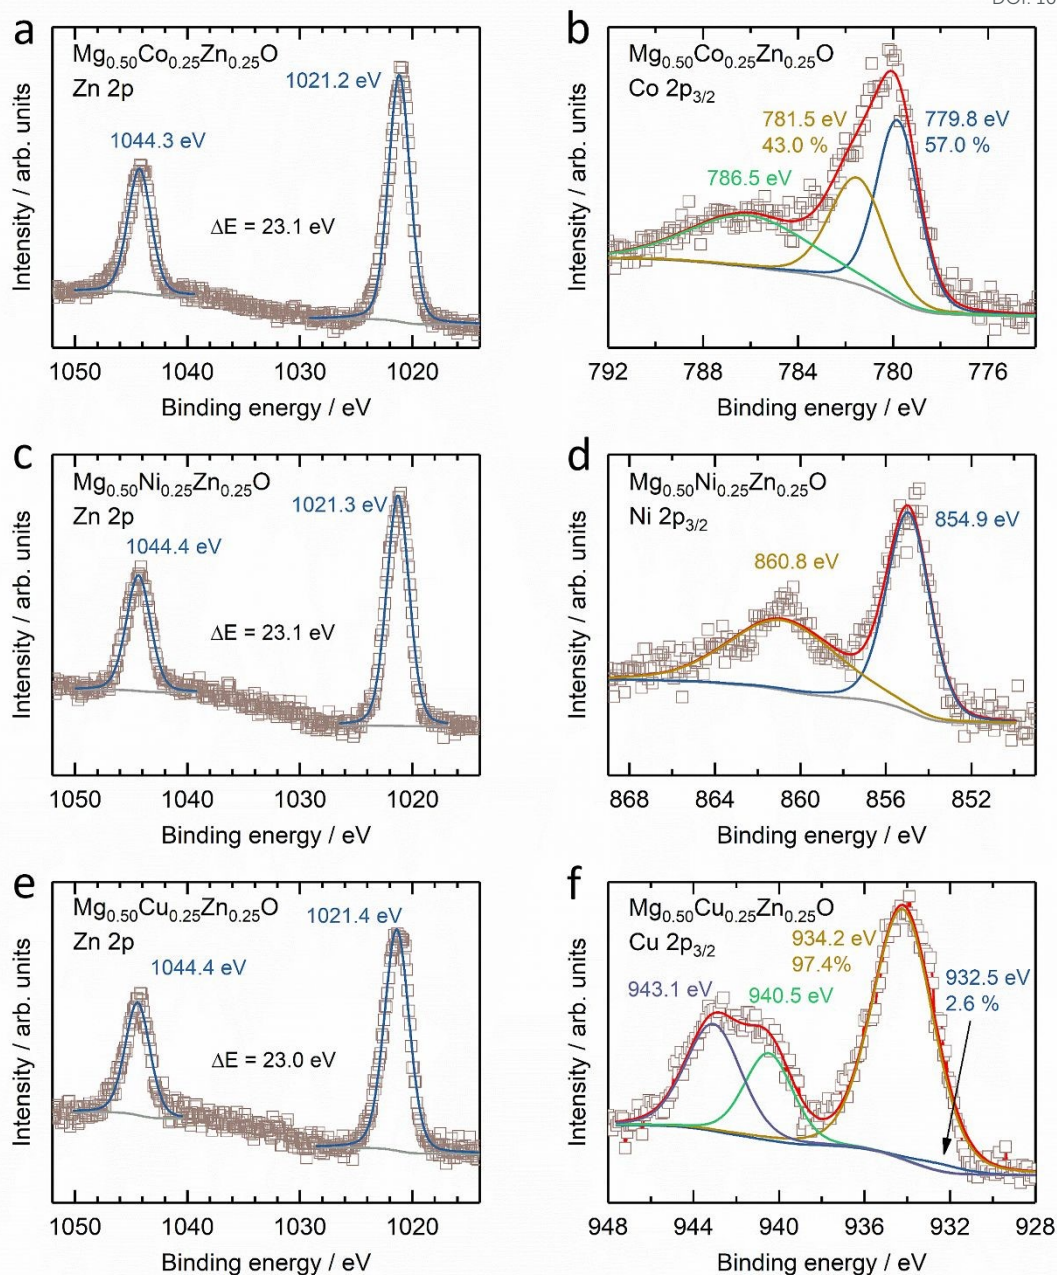


**Fig. 3.** XPS results of (a, c, e) Zn 2p and (b) Co 2p<sub>3/2</sub>, (d) Ni 2p<sub>3/2</sub> and (f) Cu 2p<sub>3/2</sub> of (a, b) Mg<sub>0.50</sub>Co<sub>0.25</sub>Zn<sub>0.25</sub>O, (c, d) Mg<sub>0.50</sub>Ni<sub>0.25</sub>Zn<sub>0.25</sub>O and (e, f) Mg<sub>0.50</sub>Cu<sub>0.25</sub>Zn<sub>0.25</sub>O.

### 3.3. Cu promoted Zn stabilization

To further investigate the effect of Cu on Zn stabilization in MgO-based rock-salt oxides, we kept the Zn fraction at 30 at% and further tune the relative ratios of Mg and Cu. From the XRD patterns in Fig. 4, Mg<sub>0.70</sub>Zn<sub>0.30</sub>O has a more obvious wurtzite ZnO phase than Mg<sub>0.75</sub>Zn<sub>0.25</sub>O in Fig. 1a. This suggests that ZnO further evolves when Zn fraction increases from 25% in Mg<sub>1-x</sub>Zn<sub>x</sub>O series. As the Cu fraction increases to 10% and 20%, the ZnO diffraction peaks become increasingly weaker, which means that Cu is effective in stabilizing Zn and inhibiting the ZnO



evolution in the rock-salt oxide, even though the amount of phase formation agent Mg decreases and is replaced by Cu. Meanwhile, an increasing (111) peak intensity can be observed, which indicates that the introduction of Cu improves the order in the [111] direction. In addition, the (200) peak becomes weaker gradually, which is caused by the Jahn-Teller distortion of  $\text{Cu}^{2+}$  ions<sup>51</sup>. The Rietveld refinements of  $\text{Mg}_{0.70}\text{Zn}_{0.30}\text{O}$ ,  $\text{Mg}_{0.60}\text{Cu}_{0.10}\text{Zn}_{0.30}\text{O}$  and  $\text{Mg}_{0.45}\text{Cu}_{0.25}\text{Zn}_{0.30}\text{O}$  can be found in Figs. S18-S20. There are no obvious attribution changes in the XPS profiles of  $\text{Mg}_{0.45}\text{Cu}_{0.25}\text{Zn}_{0.30}\text{O}$  (Fig. S21). When the Cu fraction reaches 30%, an obvious ZnO phase is observed again and a new  $\text{Cu}_2\text{MgO}_3$  impurity appears. This means that the introduction of excess Cu does not contribute to Zn stabilization in the rock-salt oxide, and on the contrary it causes  $\text{Cu}_2\text{MgO}_3$  formation, which lowers Zn solubility in the rock-salt oxides.

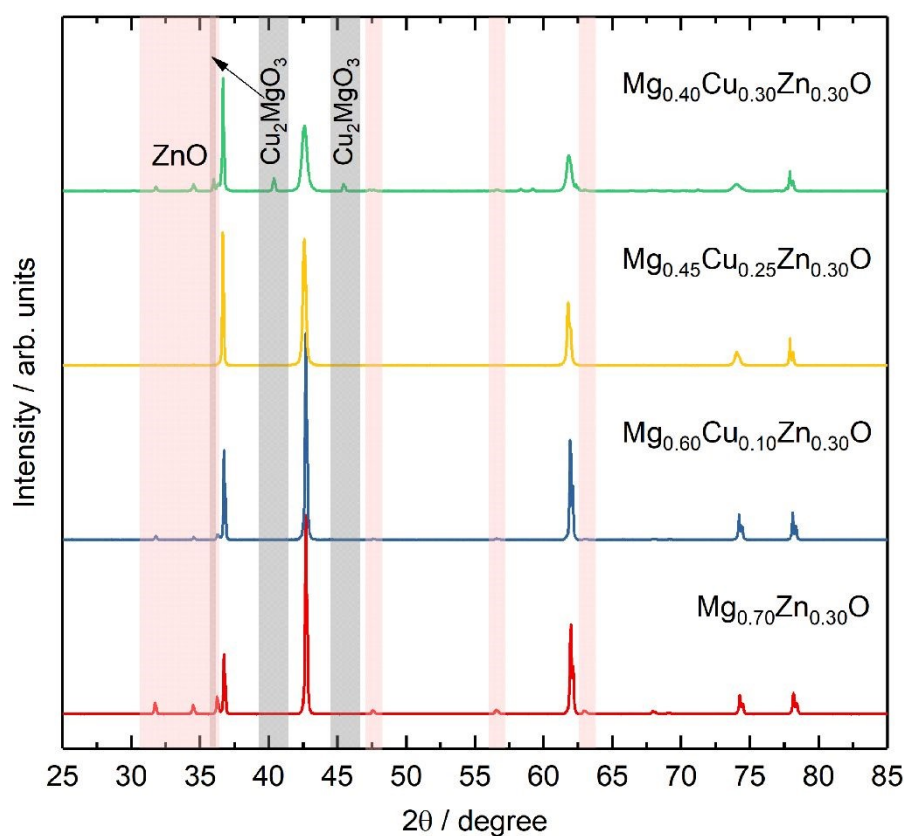

**Fig. 4.** XRD patterns of  $\text{Mg}_{0.70-x}\text{Cu}_x\text{Zn}_{0.30}\text{O}$  series.

### 3.4. Formation energy and bond length distribution

To gain deeper insights into the experimental findings, we further perform density functional theory (DFT) simulations for the three compositions:  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ ,  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ . Special quasirandom structures (SQSs) are used to model the solid solution state of these rock-salt oxides. As shown in Figs. 5a-c, the relaxed structures demonstrate significant differences. In the case of  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  (Fig. 5b), the inclusion




of Cu atoms results in noticeable lattice distortions. This distortion can be attributed to the Jahn-Teller effect induced by  $\text{Cu}^{2+}$ . The observed deviation in the oxygen positions of the relaxed structure of  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  aligns with the low intensity of the metal-oxygen peak in the EXAFS results. Conversely, the lattice distortion is found to be less profound in  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  (Fig. 5c and Fig. S22). The trend of the lattice constants obtained from the relaxed models is also consistent with our experimental observations (Fig. 5d), further strengthening the reliability of our simulations.

To investigate the influence of lattice distortions on Zn solubility in MgO, we calculated the formation energies for the substitution of Mg by Zn in the three structures mentioned above. The reference structures to obtain the formation energies are constructed by replacing all the Zn atom by Mg atoms for  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ ,  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$ ,  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.75}\text{Zn}_{0.25}\text{O}$  while keeping the atom positions of the gnat eater structures fixed. The calculated average formation energies for Zn substitution of Mg for  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ ,  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ , with respect to  $\text{Mg}_{0.75}\text{Zn}_{0.25}\text{O}$ , are -20.21 meV, 0.52 meV, and -41.31 meV, respectively (Fig. 5e). These results indicate that the inclusion of Cu or Co atoms stabilizes the solubility of Zn in MgO, while the presence of Ni has negligible effects. Furthermore, the lowest formation energy is observed for  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ , suggesting that Zn is most readily stabilized in this composition among the three samples investigated. These findings are consistent with the XRD results obtained for  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ ,  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ .





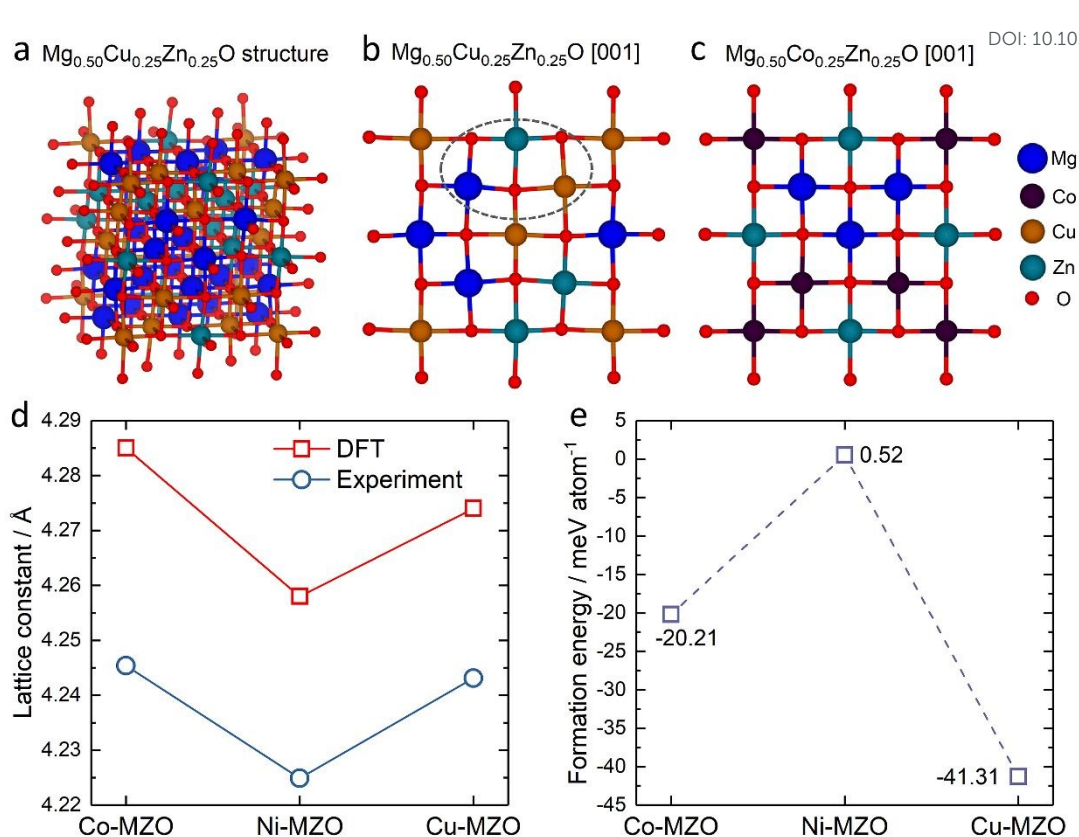

**Fig. 5.** The typical rock-salt structure generated from the high-entropy random model of (a)  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ , the slice of (b)  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  and (c)  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  viewed from [001] direction; (d) the lattice constant from the relaxed structure and the experiment (XRD patterns), and (e) the average formation energy for substituting Mg by Zn in  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  (Co-MZO),  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  (Ni-MZO) and  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  (Cu-MZO).

Apart from the different formation energies, we can also observe the change in the metal-oxygen bond length distribution in the relaxed  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ ,  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  structures (Fig. 6). In  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ , the Mg-O, Co-O and Zn-O bond lengths are distributed and concentrated between 2.10-2.15 Å, 2.13-2.18 Å, and 2.13-2.18 Å, with their average bond lengths being 2.13 Å, 2.15 Å and 2.16 Å, respectively (Figs. 6a-c). This is consistent with the order of the metal ionic radii: 0.720 Å ( $\text{Mg}^{2+}$ ) < 0.735 Å ( $\text{Co}^{2+}$ , high spin) < 0.745 Å ( $\text{Zn}^{2+}$ ). In  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  (Figs. 6d-f), the distribution ranges of the Mg-O (2.07-2.16 Å) and Zn-O (2.12-2.19 Å) bond lengths are larger than that of  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ . The Ni-O bond length distributes between around 2.09-2.15 Å, which is ascribed to the smaller radius (0.70 Å) of  $\text{Ni}^{2+}$ . In  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ , the average bond lengths for Mg-O, Ni-O and Zn-O are 2.12 Å, 2.12 Å and 2.17 Å, respectively. Interestingly, the distributions of Mg-O, Cu-




O and Zn-O bond lengths in  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  (Figs. 6g-i) are much more widespread than that in the other two materials. In particular, the Cu-O bond lengths are distributed across two separate regions, that is, 1.94-2.10 Å and 2.19-2.38 Å, which is attributed to the Jahn-Teller effects of  $\text{Cu}^{2+}$  ions. The average bond length value of Cu-O is 2.14 Å, which is smaller than that of Co-O but larger than that of Ni-O. Zn also has a more random Zn-O bond length distribution (2.01-2.31 Å, average bond of 2.17 Å) in  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ . The larger average Zn-O and Cu-O bond lengths in  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  may partially result from the large distribution range of Cu-O/Zn-O bonds. The bond lengths for Mg-O are in the range of 2.05 Å-2.22 Å with an average of 2.12 Å. Thus, Cu substitution causes a more random metal-oxygen bond length distribution, potentially improving space flexibility for Zn accommodation. However, this flexible space does not exist in the  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$ , and thus leading to a low Zn stabilization in the rock-salt oxide.

Inferring from the XRD, EXAFS and calculation results, creating a structure with long-range order and short-range disorder is crucial in stabilizing  $\text{Zn}^{2+}$  ions in the rock-salt oxide. From the perspective of the coordination environment, a properly flexible spatial environment facilitates the Zn stabilization in the rock-salt oxide. When considering the orbitals, such flexible spatial environment is caused by the splitting of  $e_g$  orbitals due to the Jahn-Teller distortion. Therefore, in our cases, the short-range disorder and flexible spatial environment produces more remarkable results than increasing configurational entropy by employing the isostructural rock-salt CoO and NiO to stabilize Zn.

View Article Online  
DOI: 10.1039/D4TA02175D




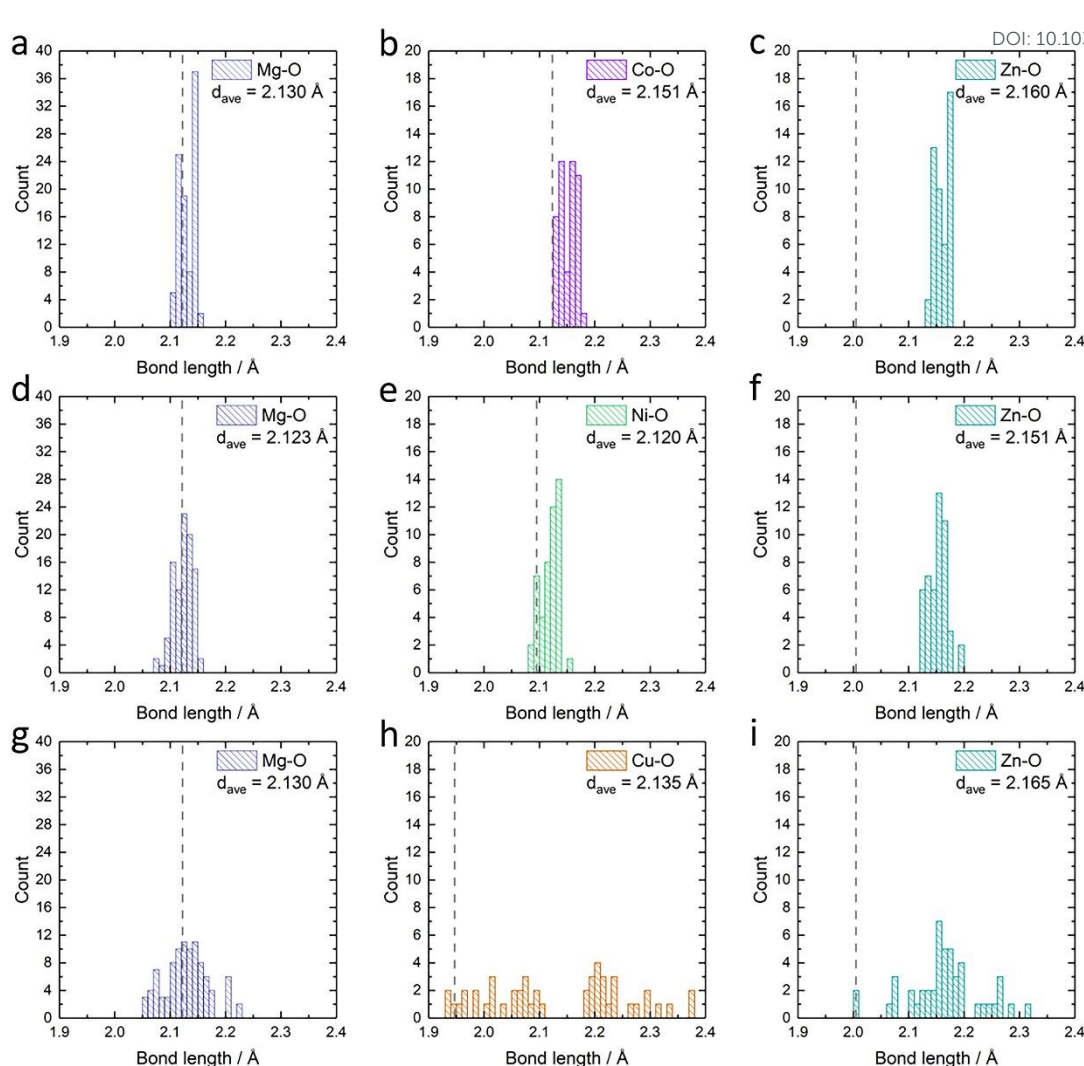


**Fig. 6.** The statistics of the metal-oxygen bond length in the relaxed structure: the bond-length of (a) Mg-O, (b) Co-O and (c) Zn-O in  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ ; the bond-length of (d) Mg-O, (e) Ni-O and (f) Zn-O in  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$ ; the bond-length of (g) Mg-O, (h) Cu-O and (i) Zn-O in  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ .  $d_{\text{ave}}$  stands for the average metal-oxygen bond length in each panel. The dash lines indicate the calculated metal-oxygen bond length for metal monoxides: rock-salt MgO in (a), (d) and (g), rock-salt CoO in (b); rock-salt NiO in (e), tenorite CuO in (h), wurtzite ZnO in (c), (f) and (i).

### 3.5. The stability of $\text{Mg}_{0.50}\text{TM}_{0.25}\text{Zn}_{0.25}\text{O}$ in alkaline solution

The stability of  $\text{Mg}_{0.50}\text{TM}_{0.25}\text{Zn}_{0.25}\text{O}$  (TM = Co, Ni and Zn) in alkaline was evaluated by soaking them in 2 M KOH at room temperature for four weeks under constant stirring. The high-entropy oxide  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$  was treated by the same method as a control sample. According to the XRD patterns of these soaked oxides as shown in Fig. 7a, no obvious impurity is observed for soaked  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$ . However, the metal



hydroxide ( $\text{Mg}(\text{OH})_2$  /  $\text{Co}(\text{OH})_2$ ) phases are observed for soaked  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}(\text{OH})_2$  and  $\text{CuO}$  phases are observed for soaked  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ . Figs. 7b-e demonstrate the atomic ratios of these oxides before and after soaking in KOH (Table S3-S10). For soaked  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$  and  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$ , no obvious change is observed compared to their raw counterparts. For soaked  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ , the Zn atomic ratio decreases from 25.7 to 7.5, indicating that the Zn is preferentially leached from  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ . Accordingly, this leads to the increase of the atomic ratios of Mg and Co. For soaked  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ , the atomic ratios of Zn and Cu decreases from 23.7 to 9.62 and 23.5 to 19.6, and accordingly, the Mg atomic ratio increases from 52.9 to 70.7, indicating the preferential leaching-out of Zn and Cu. These results suggests that  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$  and  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$ , which contain Ni, have stronger resistance to alkaline solution and remain high structure stability. It should be noted that our results do not imply that metal elements like Co and Ni are completely retained in raw materials. Instead, they indicate that the Zn and Cu are preferentially leached, reducing the structure stability. We did not test the ratio of metal elements in alkaline centrifugate, because we cannot ensure the powder does not exist in alkaline centrifugate, which could affect the leached element ratios.

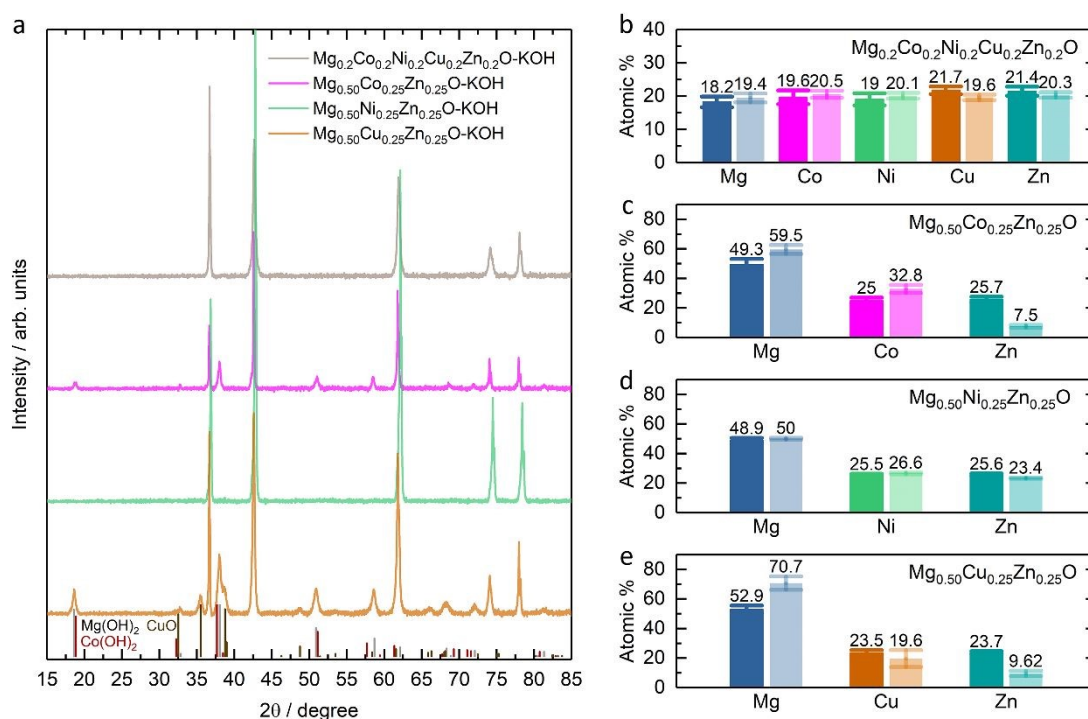


**Fig. 7.** (a) XRD patterns of  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$  and  $\text{Mg}_{0.50}\text{TM}_{0.25}\text{Zn}_{0.25}\text{O}$  (TM = Co, Ni, Cu) after soaking in 2 M KOH for four weeks, denoted as  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O-KOH}$  and  $\text{Mg}_{0.50}\text{TM}_{0.25}\text{Zn}_{0.25}\text{O-KOH}$ . XRD standard peak:  $\text{Mg}(\text{OH})_2$  refers to PDF 00-007-0239;  $\text{Co}(\text{OH})_2$  refers to PDF 00-045-0031;  $\text{CuO}$  refers to PDF 00-045-0937. Atomic percentage of



(b)  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$  and (c, d, e)  $\text{Mg}_{0.50}\text{TM}_{0.25}\text{Zn}_{0.25}\text{O}$  before and after soaking in 2 M KOH for four weeks. The bars in dark color are for the raw oxides while the light ones for the soaked samples.

From the XPS results (Figs. S23-S26), one obvious change is the ratio increase at  $\sim 531$  eV binding energy in the O 1s profile (Fig. 8) for soaked oxides, and this peak also suggests more hydroxides on the surface,<sup>63</sup> which is consistent with the hydroxide appearance from XRD profile (Fig. 7a). This phenomenon is also expected as more water molecules bound to the surface after soaking, in combination with 531 eV attribution reported by Frankcombe and Liu.<sup>68</sup> Another obvious change is the decrease of the signal-to-noise ratios of the Zn 2p profile for the soaked  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$  (Fig. S24) and  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  (Fig. S26), indicating the deduced Zn concentration on the surface. It agrees with the atomic ratio shown in Figs. 7c and 7e. In addition, the signal-to-noise ratio of the Cu 2p<sub>3/2</sub> profile for the soaked  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$  (Fig. S23) also decreases, suggesting a decreased Cu ratio on the surface. The SEM images of soaked oxides are provided in Fig. S27. The optical photographs of  $\text{Mg}_{0.50}\text{TM}_{0.25}\text{Zn}_{0.25}\text{O}$  (TM = Co, Ni, Cu) and  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$  before and after soaking in 2 M KOH for 4 weeks are also provided in Fig. S28.

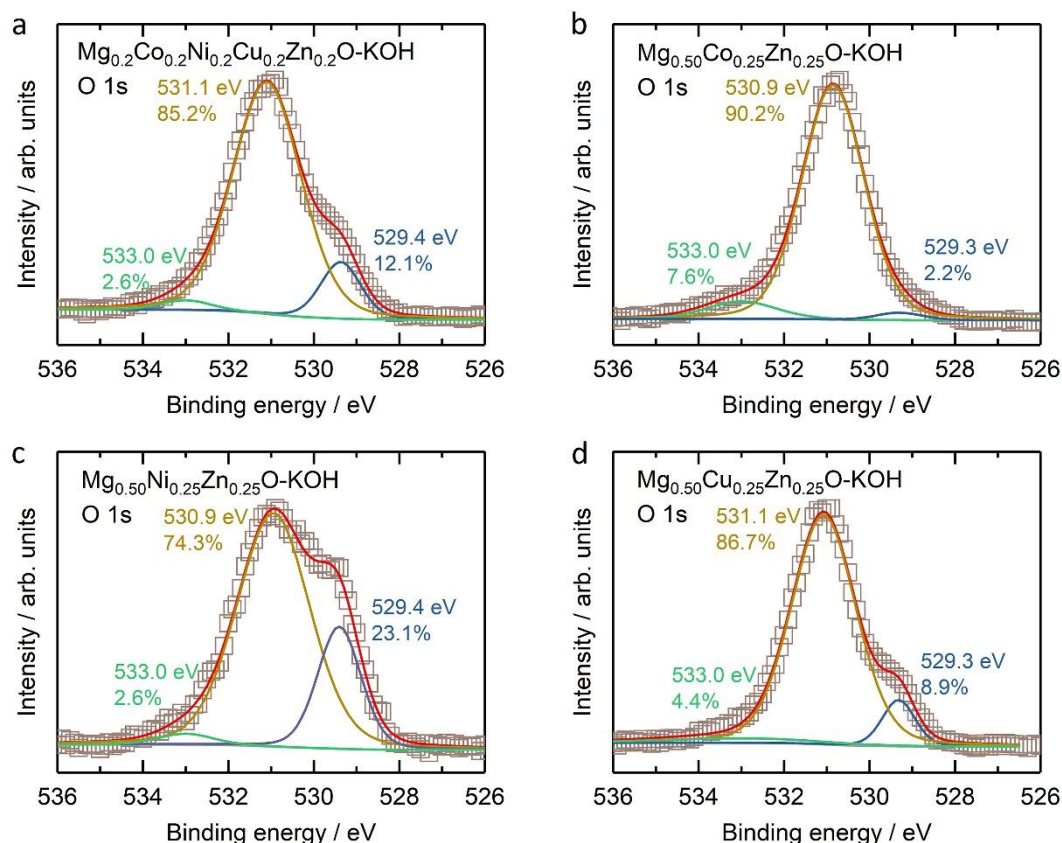

**Fig. 8.** The O 1s XPS results of (a)  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$ , (b)  $\text{Mg}_{0.50}\text{Co}_{0.25}\text{Zn}_{0.25}\text{O}$ , (c)  $\text{Mg}_{0.50}\text{Ni}_{0.25}\text{Zn}_{0.25}\text{O}$ , and (d)  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$ .

#### 4. Conclusions

In summary, we investigated the roles of Co, Ni and Cu in stabilizing Zn in the MgO-based rock-salt oxides. Experimental results demonstrate that incorporation of Co, Ni and Cu increases ZnO solubility in rock-salt MgO-ZnO system, in which Cu contributes the most to stabilizing Zn despite the absence of rock-salt CuO in nature. Simulation results show that the incorporation of Cu with the Jahn-Teller effect causes a relatively lower formation energy of Zn substitution for Mg and creates a wide metal-oxygen bond length distribution and a flexible space for Zn accommodation, which does not occur in the Co- and Ni-incorporated MgO-ZnO. More importantly, medium-entropy  $\text{Mg}_{0.50}\text{Cu}_{0.25}\text{Zn}_{0.25}\text{O}$  can also stabilize 25 at% Cu and 25 at% Zn simultaneously like high-entropy  $\text{Mg}_{0.2}\text{Co}_{0.2}\text{Ni}_{0.2}\text{Cu}_{0.2}\text{Zn}_{0.2}\text{O}$ . The Ni substitution is found effective to improve the structure stability in alkaline media. This work serves as a guide to enable metal stabilization in HEOs by means of short-range disorder and flexible space environment for rational composition design, and to enable structure stability in alkaline media by metal element selection for future applications in the energy field.

#### Author contributions

S.S., J.Z., and S.X. contributed equally to this work. S.S. and Z.W.S conceived the original concept and initiated the project. S.S. wrote the manuscript. J.Z., S.X., S.W. and Z.W.S. revised it. S.S. synthesized the materials and performed the characterization with assistance from S.X. (XANES and EXAFS), H.R.T. (TEM), F.W. (XRD), D.H.L.S. (XPS), W.Y.L. (XPS) and Y.R. (XPS). S.X. did the EXAFS fitting. J.Z. carried out the theoretical calculation and results analysis. S.W. supervised the simulation work.

#### Conflicts of interest

There are no conflicts of interest to declare.

#### Data Availability

The data supporting this article have been included as part of the Electronic Supplementary Information.

#### Acknowledgments




This work was supported by the Agency for Science, Technology and Research (Central Research Fund Award), and the A\*STAR AME IAF-PP (Grant No. A19E9a0103). We acknowledge the National Supercomputing Centre Singapore for providing the computing resource.

## References

1. A. Sarkar, B. Breitung and H. Hahn, *Scripta Materialia*, 2020, **187**, 43-48.
2. C. M. Rost, E. Sachet, T. Borman, A. Moballegh, E. C. Dickey, D. Hou, J. L. Jones, S. Curtarolo and J. P. Maria, *Nat Commun*, 2015, **6**, 8485.
3. A. Sarkar, Q. Wang, A. Schiele, M. R. Chellali, S. S. Bhattacharya, D. Wang, T. Brezesinski, H. Hahn, L. Velasco and B. Breitung, *Adv Mater*, 2019, **31**, e1806236.
4. A. Amiri and R. Shahbazian-Yassar, *Journal of Materials Chemistry A*, 2021, **9**, 782-823.
5. C. Oses, C. Toher and S. Curtarolo, *Nature Reviews Materials*, 2020, **5**, 295-309.
6. S. Schweidler, M. Botros, F. Strauss, Q. Wang, Y. Ma, L. Velasco, G. Cadilha Marques, A. Sarkar, C. Kübel, H. Hahn, J. Aghassi-Hagmann, T. Brezesinski and B. Breitung, *Nature Reviews Materials*, 2024, DOI: 10.1038/s41578-024-00654-5.
7. B. Ouyang and Y. Zeng, *Nat Commun*, 2024, **15**, 973.
8. M. V. Kante, M. L. Weber, S. Ni, I. C. G. van den Bosch, E. van der Minne, L. Heymann, L. J. Falling, N. Gauquelin, M. Tsvetanova, D. M. Cunha, G. Koster, F. Gunkel, S. Nemsak, H. Hahn, L. Velasco Estrada and C. Baeumer, *ACS Nano*, 2023, **17**, 5329-5339.
9. T. X. Nguyen, Y. C. Liao, C. C. Lin, Y. H. Su and J. M. Ting, *Advanced Functional Materials*, 2021, **31**, 2101632.
10. R. R. Katzbaer, F. M. Dos Santos Vieira, I. Dabo, Z. Mao and R. E. Schaak, *J Am Chem Soc*, 2023, **145**, 6753-6761.
11. J. Wang, S. Sun, S. Xi, Y. Sun, S. J. H. Ong, Z. W. Seh and Z. J. Xu, *The Journal of Physical Chemistry C*, 2024, **128**, 4978-4987.
12. C. Liu, J. Bi, L. Xie, X. Gao and J. Rong, *Journal of Energy Storage*, 2023, **71**.
13. S. Sun, C. Dai, P. Zhao, S. Xi, Y. Ren, H. R. Tan, P. C. Lim, M. Lin, C. Diao, D. Zhang, C. Wu, A. Yu, J. C. J. Koh, W. Y. Lieu, D. H. L. Seng, L. Sun, Y. Li, T. L. Tan, J. Zhang, Z. J. Xu and Z. W. Seh, *Nat Commun*, 2024, **15**, 260.
14. A. Sarkar, L. Velasco, D. Wang, Q. Wang, G. Talasila, L. d. Biasi, C. Kübel, T. Brezesinski, S. S. Bhattacharya, H. Hahn and B. Breitung, *Nature Communications*, 2018, **9**, 3400.
15. Q. Wang, A. Sarkar, Z. Li, Y. Lu, L. Velasco, S. S. Bhattacharya, T. Brezesinski, H. Hahn and B. Breitung, *Electrochemistry Communications*, 2019, **100**, 121-125.
16. Z. Lun, B. Ouyang, D. H. Kwon, Y. Ha, E. E. Foley, T. Y. Huang, Z. Cai, H. Kim, M. Balasubramanian, Y. Sun, J. Huang, Y. Tian, H. Kim, B. D. McCloskey, W. Yang, R. J. Clement, H. Ji and G. Ceder, *Nat Mater*, 2021, **20**, 214-221.
17. F. Liu, M. Yu, X. Chen, J. Li, H. Liu and F. Cheng, *Chinese Journal of Catalysis*, 2022, **43**, 122-129.
18. N. Qiu, H. Chen, Z. Yang, S. Sun, Y. Wang and Y. Cui, *Journal of Alloys and Compounds*, 2019, **777**, 767-774.
19. P. Ghigna, L. Airoidi, M. Fracchia, D. Callegari, U. Anselmi-Tamburini, P. D'Angelo, N. Pianta, R. Ruffo, G. Cibin, D. O. de Souza and E. Quartarone, *ACS Appl Mater Interfaces*, 2020, **12**, 50344-50354.



20. K. Wang, W. Hua, X. Huang, D. Stenzel, J. Wang, Z. Ding, Y. Cui, Q. Wang, H. Ehrenberg, B. Breitung, C. Kubel and X. Mu, *Nat Commun*, 2023, **14**, 1487. View Article Online  
DOI: 10.1039/D4TA02175D
21. E. Lokcu, C. Toparli and M. Anik, *ACS Appl Mater Interfaces*, 2020, **12**, 23860-23866.
22. X. Liu, Y. Xing, K. Xu, H. Zhang, M. Gong, Q. Jia, S. Zhang and W. Lei, *Small*, 2022, **18**, e2200524.
23. M. Fracchia, M. Coduri, M. Manzoli, P. Ghigna and U. A. Tamburini, *Nature Communications*, 2022, **13**, 2977
24. S. S. Aamlid, M. Oudah, J. Rottler and A. M. Hallas, *J Am Chem Soc*, 2023, **145**, 5991-6006.
25. M. Brahlek, M. Gazda, V. Keppens, A. R. Mazza, S. J. McCormack, A. Mielewczyk-Gryń, B. Musico, K. Page, C. M. Rost, S. B. Sinnott, C. Toher, T. Z. Ward and A. Yamamoto, *APL Materials*, 2022, **10**, 110902.
26. K. Chen, J. Ma, H. Wang, C. Li and L. An, *Ceramics International*, 2021, **47**, 9979-9983.
27. J. E. Jaffe, R. Pandey and A. B. Kunz, *Phys Rev B Condens Matter*, 1991, **43**, 14030-14034.
28. S. R. Kelly, X. Shi, S. Back, L. Vallez, S. Y. Park, S. Siahrostami, X. Zheng and J. K. Nørskov, *ACS Catalysis*, 2019, **9**, 4593-4599.
29. J. Pfrommer, M. Lublow, A. Azarpira, C. Gobel, M. Lucke, A. Steigert, M. Pogrzeba, P. W. Menezes, A. Fischer, T. Schedel-Niedrig and M. Driess, *Angew Chem Int Ed Engl*, 2014, **53**, 5183-5187.
30. M. R. Shakil, A. M. El-Sawy, H. Tasnim, A. G. Meguerdichian, J. Jin, J. P. Dubrosky and S. L. Suib, *Inorg Chem*, 2018, **57**, 9977-9987.
31. R. Subhash Kanase, G. Muluaalem Zewdie, M. Arunachalam, J. Badiger, S. Abdelfattah Sayed, K.-S. Ahn, J.-S. Ha, U. Sim, H. Shin and S. Hyung Kang, *Journal of Energy Chemistry*, 2024, **88**, 71-81.
32. X. Jiang, F. Cai, D. Gao, J. Dong, S. Miao, G. Wang and X. Bao, *Electrochemistry Communications*, 2016, **68**, 67-70.
33. G. Zhang, S. Hou, H. Zhang, W. Zeng, F. Yan, C. C. Li and H. Duan, *Adv Mater*, 2015, **27**, 2400-2405.
34. W. Chang, J.-W. Choi, J.-C. Im and J. K. Lee, *Journal of Power Sources*, 2010, **195**, 320-326.
35. A. J. Laghari, U. Aftab, A. Tahira, A. A. Shah, A. Gradone, M. Y. Solangi, A. H. Samo, M. kumar, M. I. Abro, M. w. Akhtar, R. Mazzaro, V. Morandi, A. M. Alotaibi, A. Nafady, A. Infantes-Molina and Z. H. Ibupoto, *International Journal of Hydrogen Energy*, 2023, **48**, 12672-12682.
36. X. He, J. Tan, J. Wei, F. Yin, B. Chen, X. Liang and G. Li, *Applied Surface Science*, 2020, **508**, 144758.
37. Y.-z. Su, Q.-z. Xu, Q.-s. Zhong, C.-j. Zhang, S.-t. Shi and C.-w. Xu, *Materials Research Bulletin*, 2015, **64**, 301-305.
38. C. Xu, P. K. Shen, X. Ji, R. Zeng and Y. Liu, *Electrochemistry Communications*, 2005, **7**, 1305-1308.
39. H. Sclar, O. Haik, T. Menachem, J. Grinblat, N. Leifer, A. Meitav, S. Luski and D. Aurbach, *Journal of The Electrochemical Society*, 2012, **159**, A228-A237.
40. Y. Wang, Y.-F. Zhang, H.-R. Liu, S.-J. Yu and Q.-Z. Qin, *Electrochimica Acta*, 2003, **48**, 4253-4259.
41. B. Xu, H. Shen, J. Ge and Q. Tang, *Applied Surface Science*, 2021, **546**.
42. J. S. Gnanaraj, V. G. Pol, A. Gedanken and D. Aurbach, *Electrochemistry Communications*, 2003, **5**, 940-945.





43. A. van de Walle, P. Tiwary, M. de Jong, D. L. Olmsted, M. Asta, A. Dick, D. Shin, Y. Wang, L. Q. Chen and Z. K. Liu, *Calphad*, 2013, **42**, 13-18.
44. G. Kresse and J. Hafner, *Phys Rev B Condens Matter*, 1993, **47**, 558-561.
45. G. Kresse and J. Hafner, *Phys Rev B Condens Matter*, 1994, **49**, 14251-14269.
46. G. Kresse and D. Joubert, *Physical Review B*, 1999, **59**, 1758-1775.
47. J. Hubbard, *Proceedings of the Royal Society of London. Series A, Mathematical and Physical Sciences*, 1963, **276**, 238-257.
48. S. L. Dudarev, G. A. Botton, S. Y. Savrasov, C. J. Humphreys and A. P. Sutton, *Physical Review B*, 1998, **57**, 1505-1509.
49. G. C. Moore, M. K. Horton, A. M. Ganose, M. Siron, E. Linscott, D. D. O'Regan and K. A. Persson, *arXiv:2201.04213*, 2022, DOI: <https://doi.org/10.48550/arXiv.2201.04213>.
50. R. D. Shannon and C. T. Prewitt, *Acta Crystallographica*, 1969, **B25**, 925-946.
51. D. Berardan, A. K. Meena, S. Franger, C. Herrero and N. Dragoe, *Journal of Alloys and Compounds*, 2017, **704**, 693-700.
52. M. A. Peck and M. A. Langell, *Chemistry of Materials*, 2012, **24**, 4483-4490.
53. B. K. Teo, EXAFS: Basic Principles and Data Analysis, Springer Berlin, Heidelberg, 1986, Chapter 6 Data Analysis in Practice, 124.
54. J. Sushil, A. Kumar, A. Gautam and M. I. Ahmad, *Materials Chemistry and Physics*, 2021, **259**, 124014.
55. O. J. Marques, C. Chen, E. V. Timofeeva and C. U. Segre, *Journal of Power Sources*, 2023, **564**, 232852.
56. C. M. Rost, Z. Rak, D. W. Brenner and J. P. Maria, *Journal of the American Ceramic Society*, 2017, **100**, 2732-2738.
57. A. Rodrigues, M. d. C. M. Alves and J. Morais, *Materials and Design*, 2018, **142**, 240-246.
58. A. N. Baranov, P. S. Sokolov, V. A. Tafeenko, C. Lathe, Y. V. Zubavichus, A. A. Veligzhanin, M. V. Chukichev and V. L. Solozhenko, *Chemistry of Materials*, 2013, **25**, 1775-1782.
59. M. C. Biesinger, B. P. Payne, A. P. Grosvenor, L. W. M. Lau, A. R. Gerson and R. S. C. Smart, *Applied Surface Science*, 2011, **257**, 2717-2730.
60. J. Yang, H. Liu, W. N. Martens and R. L. Frost, *The Journal of Physical Chemistry C*, 2010, **114**, 111-119.
61. Y. Lykhach, S. Piccinin, T. Skala, M. Bertram, N. Tsud, O. Brummel, M. Farnesi Camellone, K. Beranova, A. Neitzel, S. Fabris, K. C. Prince, V. Matolin and J. Libuda, *J Phys Chem Lett*, 2019, **10**, 6129-6136.
62. K. Tanwar, D. S. Gyan, S. Bhattacharya, S. Vitta, A. Dwivedi and T. Maiti, *Physical Review B*, 2019, **99**, 174105.
63. N. S. McIntyre and M. G. Cook, *Analytical Chemistry*, 1975, **47**, 2208-2213.
64. K. J. Gaskell, A. Starace and M. A. Langell, *The Journal of Physical Chemistry C*, 2007, **111**, 13912-13921.
65. S. Hüfner, Photoelectron Spectroscopy Principles and Applications, Springer Berlin, Heidelberg, 2003, Chapter 3 Charge-Excitation Final States: Satellites, 129-130.
66. S. Altieri, L. H. Tjeng, A. Tanaka and G. A. Sawatzky, *Physical Review B*, 2000, **61**, 13403-13409.
67. J. C. C. Fan and J. B. Goodenough, *Journal of Applied Physics*, 1977, **48**, 3524-3531.
68. T. J. Frankcombe and Y. Liu, *Chemistry of Materials*, 2023, **35**, 5468-5474.



**Data Availability**

View Article Online  
DOI: 10.1039/D4TA02175D

The data supporting this article have been included as part of the Electronic Supplementary Information.

