


Nanoscale

rsc.li/nanoscale



ISSN 2040-3372

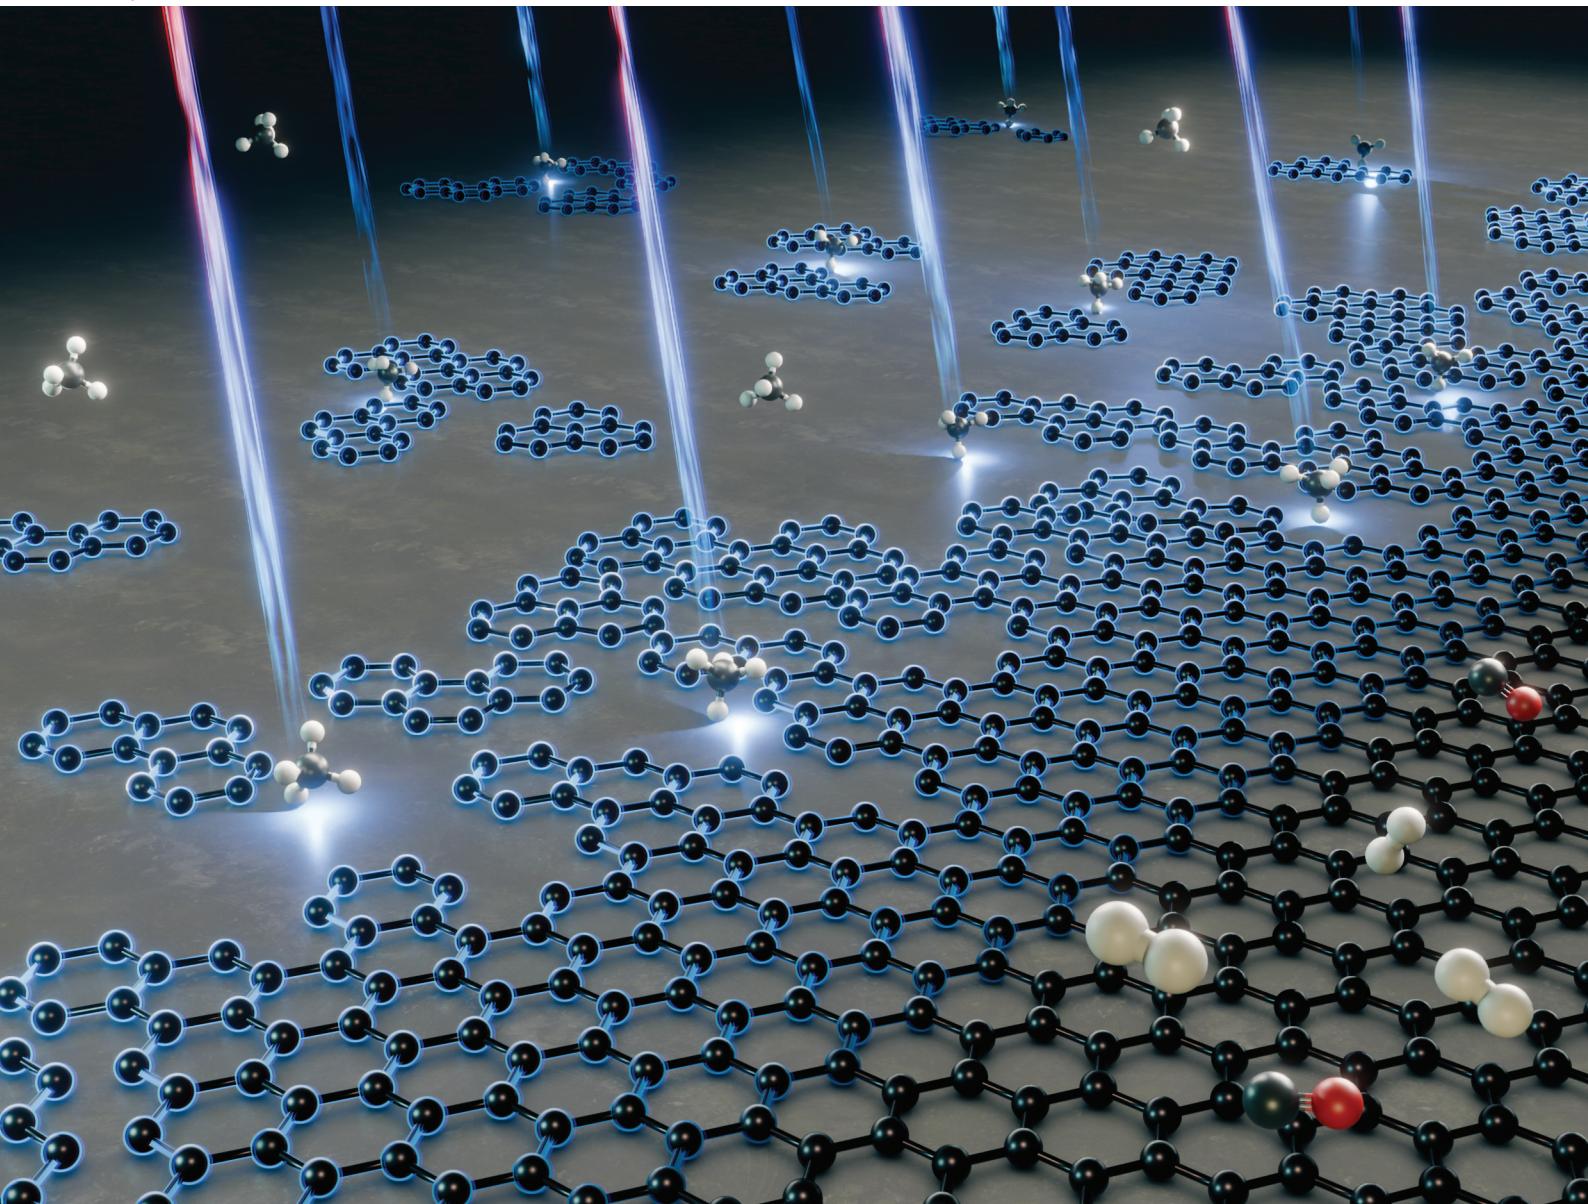

Cite this: *Nanoscale*, 2025, **17**, 13646

Mechanism of methane activation and graphene growth on oxide ceramics

Hanzhang Zhou, ^a Mengxuan Zhang, ^a Takeharu Yoshii, ^{*a} Devis Di Tommaso ^{b,c} and Hirotomo Nishihara ^{*a,d}

Three-dimensional (3D) graphene materials have attracted significant attention across various fields, including energy storage and catalysis, due to their exceptional properties such as developed nanoporosity, corrosion resistance, electrical conductivity, and mechanical flexibility. The first step in synthesizing nanoporous 3D graphene involves the generation of the graphene framework through the decomposition of methane at high temperatures on thermally stable oxide ceramics. Thus, a thorough understanding of the reaction mechanism involved in this initial step is crucial. This article reviews recent advancements in elucidating the mechanisms of methane activation and subsequent graphene growth on various types of oxide ceramics, including alumina (Al_2O_3), magnesia (MgO), calcium oxide (CaO), and silica (SiO_2).

Received 8th February 2025,
Accepted 9th April 2025

DOI: 10.1039/d5nr00569h

rsc.li/nanoscale

1. Introduction

Graphene is a remarkable carbon material characterized by a two-dimensional, monolayer structure in which carbon atoms are arranged in a hexagonal lattice *via* sp^2 hybridization.¹ As one of the thinnest and lightest materials known, graphene exhibits exceptional properties, including high electrical conductivity, out-

standing electron mobility ($2.5 \times 10^5 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$),² a large specific surface area ($2627 \text{ m}^2 \text{ g}^{-1}$),³ and remarkable thermal conductivity (over 3000 W mK^{-1}).⁴ Its unique characteristics make it highly versatile for a wide range of advanced applications, including biosensors,⁵ solar cell electrodes,⁶ and photocatalysts.⁷ Recently, graphene has become capable of being mass-produced at a relatively low cost, enhancing its practical value. Spherical molecules composed of sp^2 carbon, known as fullerenes,⁸ and tubular structures, referred to as carbon nanotubes,^{9,10} are zero-dimensional and one-dimensional graphene-related structures, respectively, each possessing unique characteristics distinct from two-dimensional graphene. Meanwhile, steady progress has recently been made in the synthesis of three-dimensional (3D) graphene structures, theoretically designed by incorporating heptagonal and octagonal rings into carbon hexagonal networks.^{11,12} Among these developments, the “Graphene MesoSponge®

^aInstitute of Multidisciplinary Research for Advanced Materials, Tohoku University, 2-1-1, Katahira, Aoba-ku, Sendai, 980-8577, Japan.

E-mail: takeharu.yoshii.b3@tohoku.ac.jp, hirotomo.nishihara.b1@tohoku.ac.jp

^bDepartment of Chemistry, Queen Mary University of London, London E1 4NS, UK

^cDigital Environment Research Institute, Queen Mary University of London, London E1 1HH, UK

^dAdvanced Institute for Materials Research (WPI-AIMR), Tohoku University, 2-1-1, Katahira, Aoba-ku, Sendai, 980-8577, Japan



Hanzhang Zhou

Hanzhang Zhou (b. 2001) is currently a Ph.D. candidate in Chemical Engineering at Tohoku University, Japan, under the supervision of Prof. Hirotomo Nishihara. Her research focuses on the mechanism of low-temperature CVD on inorganic substrates.



Mengxuan Zhang

Mengxuan Zhang (b. 1996) is currently a Ph.D. candidate in Chemical Engineering at Tohoku University, Japan, under the supervision of Prof. Hirotomo Nishihara. Her research focuses on the mechanism of acetylene CVD at low temperatures on metal oxides and the synthesis of graphene quantum dots via the CVD method.



(GMS)¹³ recently developed by the authors, is a novel mesoporous material that strongly reflects the characteristic properties of graphene, such as high specific surface area, electrical conductivity, corrosion resistance, lightweight nature, and mechanical flexibility. It holds great potential for applications in various fields, including energy storage,^{14,15} heat pumps,¹⁶ and catalyst supports.^{17,18}

This minireview primarily highlights recent advancements in the initial stage of GMS synthesis, specifically the chemical vapor deposition (CVD) process. The entire synthesis process of GMS will first be outlined, followed by an in-depth discussion of the CVD process, with an emphasis on the mechanism of graphene growth on the surface of oxide ceramics. Note that in this minireview, “CH₄ activation” refers to the initial catalytic weakening of C–H bonds, while “CH₄ decomposition” encompasses the entire process of CH₄ breakdown into carbon, either catalytic or non-catalytic thermal pathways.

2. Synthesis of three-dimensional graphene

Graphene can be synthesized by various methods, including mechanical cleavage,¹ chemical exfoliation,^{19,20} epitaxial growth on SiC surfaces,²¹ and CVD.²² Among these, CVD is regarded as one of the most promising approaches for fabricating graphene-based 3D nanostructures. Since CVD promotes graphene growth along the substrate surface, removing the substrate after performing CVD on a 3D nanostructured substrate results in 3D graphene with a corresponding morphology.^{23–25} The substrate used in CVD is referred to as the “template”. CVD needs to be conducted at high temperatures, typically around 600–900 °C to produce high-quality gra-

phene. Consequently, it is challenging to use metal nanostructures with a low melting point as templates, underscoring the need for templates with higher heat resistance. On the other hand, oxide ceramics exhibit excellent heat resistance and serve as templates even at CVD temperatures, allowing for relatively straightforward control over 3D nanostructures.

When Al₂O₃ or zeolite is used as a catalyst for the organic compound conversion reactions at high temperatures, polycyclic aromatic hydrocarbons (coke) are produced as by-products and the catalytic activity is reduced. This phenomenon is widely known as “coking”. Coking causes poisoning of catalysts, and therefore, most researchers tried to avoid coking. On the other hand, Kyotani’s group pioneered the utilization of coking reactions for synthesizing templated carbons.^{26,27} For example, intentional coke deposition, *i.e.*, CVD, inside the three-dimensional network pores of zeolites results in zeolite-templated carbon (ZTC),²⁷ consisting of a three-dimensional framework of single-layer graphene.^{25,28} ZTC is, to the best of the authors’ knowledge, the most pioneering 3D graphene structure and continues to be actively studied worldwide.³ However, ZTCs have low chemical stability due to the large amount of graphene edge sites. It will quickly degrade when applied to batteries and other devices.³

GMS overcomes this weakness of ZTC by removing edges to the maximum extent possible through a graphene fusion (zipping) reaction,²⁹ achieving chemical stability superior to that of carbon nanotubes.^{14,30} Fig. 1 illustrates the formation of GMS. The typical synthesis of GMS begins with a CVD process using Al₂O₃ and MgO nanoparticles as spherical templates and CH₄ as the carbon source.³¹ After the CVD, the template surfaces are uniformly coated with a thin carbon layer, approximately equivalent to a single graphene layer. Subsequent chemical etching removes the templates, yielding a carbon mesosponge (CMS) with spherical mesopores. The CMS



Takeharu Yoshii

Takeharu Yoshii (b. 1992) received his Ph.D. degree in Engineering from Osaka University in 2020 under the supervision of Professor Hiromi Yamashita. That same year, he joined the Institute of Multidisciplinary Research for Advanced Materials (IMRAM) at Tohoku University as an Assistant Professor, working with Professor Hirotomo Nishihara. He was promoted to Associate Professor in 2025. Since 2023,

he has also served as a researcher in the JST PREST “Future Materials” program. His research has focused on the design and synthesis of nanostructured heterogeneous catalysts. Recently, his interests have expanded to include the synthesis, analysis, and application of carbon materials.



Devis Di Tommaso

Devis Di Tommaso (b. 1977) received his Ph.D. in Computational Chemistry from the University of Trieste, Italy, with Professor Piero Decleva in 2006. After completing postdoctoral research positions in the UK at the Royal Institution of Great Britain with Professor Richard Catlow and at University College London with Professor Nora de Leeuw, he joined Queen Mary University of London in 2013 as a Lecturer.

He was promoted to Senior Lecturer in 2020 and to Reader in 2024. His research group develops and applies computational methods based on quantum, classical, and machine learning approaches to study the conversion of small molecules into value-added materials.



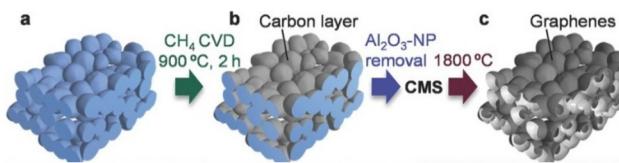


Fig. 1 A schematic of the synthesis of GMS. (a) Al_2O_3 -nanoparticles (NP) as a nanosized substrate for CVD. (b) Carbon-coated Al_2O_3 -NP. (c) GMS prepared by high-temperature treatment ($1800\text{ }^\circ\text{C}$) of CMS obtained by removing Al_2O_3 -NP from carbon-coated Al_2O_3 -NP. Reprinted with permission.¹³ Copyright Wiley 2016.

is then subjected to heat treatment at $1800\text{ }^\circ\text{C}$, promoting the zipping reaction to form a graphene framework with a minimal number of edge sites. Thus, graphene growth on oxide ceramics represents the first critical step in GMS synthesis. However, the detailed reaction mechanisms have been largely unknown. Recent studies have advanced our understanding of graphene growth mechanisms on various types of oxide ceramics, which are discussed in detail in the following sections. Note that thermal stability is a key factor in selecting oxide templates, particularly the ability to maintain surface area and crystal structure under high-temperature conditions above $600\text{ }^\circ\text{C}$. This minireview focuses on thermally stable oxides, including as Al_2O_3 , MgO , CaO , and SiO_2 . As an example using a different template, graphene has been synthesized at $700\text{ }^\circ\text{C}$ using CeO_2 under photo-assisted conditions.³²

3. Mechanism of graphene growth on ceramic oxide surface

3.1. Aluminium oxide (Al_2O_3) and magnesium oxide (MgO)


The synthesis of templated carbon utilizing the coking effect on Al_2O_3 had been previously reported by Kyotani *et al.*²⁶



Hirotomo Nishihara

3DC. As the Chief Science Officer, he is dedicated to the industrialization of a novel porous carbon material, graphene mesosponge, which he developed. His research interests include nanoporous materials and carbon-based materials.

Accordingly, in the development of GMS, naturally aggregated $\gamma\text{-Al}_2\text{O}_3$ nanoparticles were initially employed as a 3D template framework.¹³ To form highly crystalline graphene through CVD, thermally stable CH_4 , which allows for higher reaction temperatures, was used as the carbon source. However, the removal of Al_2O_3 template after CVD required either high temperature alkaline melting or hydrofluoric acid (HF) treatment, making the process both costly and environmentally burdensome. In response, the authors explored alternative templates and found that MgO , which can be dissolved in hydrochloric acid (HCl), is also suitable for GMS synthesis.³³ Interestingly, the following reaction, where CH_4 is converted to graphene at high temperatures, occurs on both the solid acid ($\gamma\text{-Al}_2\text{O}_3$) and the solid base (MgO).



Thus, the CVD reaction shown in eqn (1) likely proceeds *via* a mechanism independent of solid acid or base effects.

To investigate this, a detailed analysis of the CVD reaction was performed on the surfaces of both materials.³³ Fig. 2a compares graphene growth rates on both catalyst surfaces at various temperatures. Here, the weight change resulting from graphene deposition on the template during the CVD reaction was measured using the thermogravimetric analyser (TG). The weight gain was then converted to the average number of graphene layers by dividing it by the specific surface area of the template. On either solid surface, the growth rate of the first graphene layer was two to three times faster than that of the second and subsequent layers. The activation energy for forming the first graphene layer was 114 kJ mol^{-1} for $\gamma\text{-Al}_2\text{O}_3$ and 134 kJ mol^{-1} for MgO ,³³ both of which are significantly lower than the activation energy for non-catalytic CH_4 decomposition ($370\text{--}433\text{ kJ mol}^{-1}$).³⁴ In contrast, the activation energy for forming subsequent layers was higher, at 234 kJ mol^{-1} for $\gamma\text{-Al}_2\text{O}_3$ and 210 kJ mol^{-1} for MgO activation energies, respectively.³³ These values are comparable to the activation energy for CH_4 decomposition on carbon black ($205\text{--}236\text{ kJ mol}^{-1}$),³⁵ suggesting that subsequent graphene layers form on the first layer. This sequential graphene growth mechanism makes it easy to achieve the uniform coating of single-layer graphene.

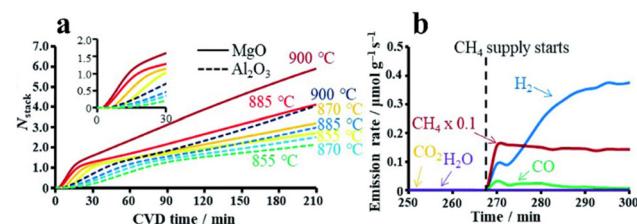


Fig. 2 Analysis of graphene growth reactions *via* CVD using CH_4 as a precursor on $\gamma\text{-Al}_2\text{O}_3$ and MgO . (a) Plot of the number of graphene layers formed versus CVD reaction time. (b) Gas analysis during the CVD reaction on MgO . CH_4 was introduced to preheated MgO at $900\text{ }^\circ\text{C}$ at the time labelled "CH₄ supply starts". Reprinted with permission.³³ Copyright Royal Society of Chemistry 2021.



Furthermore, as shown in the inset of Fig. 2a, an induction period of 5–10 min was observed from the time the template was exposed to CH_4 (CVD time = 0) to the onset of carbon deposition. Gas analysis during this induction period (Fig. 2b) detected not only the CH_4 precursor and the H_2 product but also the release of CO , a common feature observed on both Al_2O_3 and MgO . These results indicate that CH_4 extracts oxygen from the surfaces of $\gamma\text{-Al}_2\text{O}_3$ or MgO in the form of CO , generating oxygen vacancies that serve as active sites for converting CH_4 into graphene. Notably, similar CVD reactions were observed on $\theta\text{-Al}_2\text{O}_3$ as well.³⁶ These insights into the formation of oxygen vacancy sites and their role in the activation of CH_4 were further corroborated by density functional theory (DFT) calculations. Fig. 3 summarizes the mechanism of graphene formation on Al_2O_3 and MgO surfaces.³³

The initial step of graphene nucleation on the $\gamma\text{-Al}_2\text{O}_3$ surface was studied in more depth by Di Tommaso and co-workers using computational methods.³⁷ The process begins with C–H activation, involving proton abstraction by surface oxygen atoms, followed by β -hydrogen elimination, leading to the formation of H_2 . Fig. 4a shows the energy diagram for dehydrogenation on the most active (100) surface of $\gamma\text{-Al}_2\text{O}_3$. While the removal of two hydrogen atoms from CH_4 to form the CH_2 adsorbate species (CH_2^*) proceeds with a low energy barrier, the removal of the third hydrogen atom faces a significantly higher energy barrier. This suggests that CH_2^* is a key intermediate in the graphene nucleation process. Furthermore, the energy diagram for the coupling reaction of CH_2^* on the (100) surface (Fig. 4b) demonstrates that CH_2^* readily grows into $\text{C}_n\text{H}_{2n}^*$ species ($n = 2\text{--}6$). The length of C–C bond length in the $\text{C}_n\text{H}_{2n}^*$ species on the $\gamma\text{-Al}_2\text{O}_3$ surface expands with increasing chain length. During the early stages of nucleation, the unsaturated CH_2^* groups at both ends of the carbon chain strongly adsorb to the catalyst surface, while

the middle part detaches from the surface, forming a loop-like structure, contributing to the nucleation of graphene.

Di Tommaso and co-workers also adopted a computational approach based on DFT calculations with machine learning forcefield molecular dynamics simulations to investigate the stability and growth investigation of larger graphene clusters, C_n ($n = 16\text{--}26$), on MgO .³⁸ Among the various C_n clusters examined, the C_{21} cluster, which features a bowl-shaped molecular structure with three pentagons and three hexagons alternately arranged around a central hexagon, exhibited unique stability on MgO surface. Furthermore, the high electron density at the central hexagon suggests that this cluster acts as a low-mobility nucleation site for graphene growth during CVD. Additionally, it was found that the stability of the C_{21} cluster is enhanced when impurities such as Si, Mn, Fe, Ca, or Al are doped onto the MgO surface. These computational results suggest that graphene clusters formed in the early stages of CVD tend to adopt specific structures, such as the C_{21} cluster.

3.2. Calcium oxide (CaO)

CaO is a more cost-effective template compared to Al_2O_3 and MgO , as it can be readily produced through the low-cost thermal decomposition of enriched calcium carbonate (CaCO_3) and easily removed using hydrochloric acid (HCl). Our group has already demonstrated the synthesis of GMS using CaO nanoparticles as templates.³⁹ Additionally, CaO offers higher catalytic activity for CH_4 decomposition compared to Al_2O_3 and MgO , allowing CVD to occur at lower temperatures.

A detailed study of the mechanism of graphene formation via CVD using CH_4 as a precursor on CaO template was conducted through experimental and computational methods.⁴⁰ DFT calculations revealed that the stepped oxygen sites on the CaO (110) surface possess significantly lower energy barriers for CH_4 dehydrogenation reactions, regardless of the presence of oxygen vacancies (Fig. 5). Specifically, even without oxygen vacancies, the C–H cleavage step of CH_4 to form CH_3^* and CH_2^* proceeds spontaneously, and the resulting CH_2^* species can subsequently transform into graphene. Indeed, gas emission in the early stage of CVD indicates that, unlike Al_2O_3 and MgO , there is no induction period on the CaO template. That is, graphene formation begins immediately upon CH_4 contacting the CaO surface.⁴⁰

Although the CaO surface is active even without oxygen vacancies, analysis of the emission gas composition during CVD reveals that CaO releases more CO than Al_2O_3 and MgO . This release continues even after the graphene layer reaches a single layer in thickness. The total CO emission during CVD on CaO reaches $4.04 \mu\text{mol m}^{-2}$.⁴⁰ In contrast, CO desorption from Al_2O_3 and MgO terminates before the graphene layer reaches 0.5 layers, with total emissions of only 0.52 and $1.37 \mu\text{mol m}^{-2}$, respectively. These findings indicate that, on the CaO surface, the decomposition of CH_4 leading to graphene growth and the desorption of surface oxygen as CO occur simultaneously. Furthermore, CO desorption from the CaO surface persists even after the CaO surface is completely

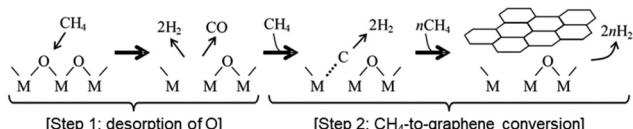


Fig. 3 Mechanism of graphene formation via CVD using CH_4 as a precursor on $\gamma\text{-Al}_2\text{O}_3$ and MgO ($\text{M} = \text{Al}$ or Mg).

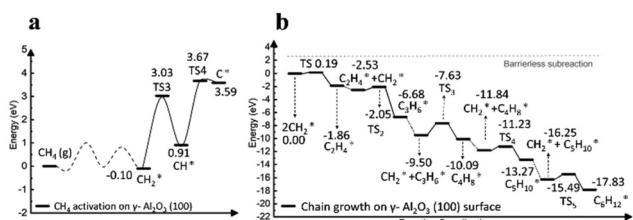


Fig. 4 Energy profiles of (a) the complete CH_4^* dehydrogenation and (b) the formation of $\text{C}_n\text{H}_{2n}^*$ ($n = 2\text{--}6$) species via CH_2^* coupling on the $\gamma\text{-Al}_2\text{O}_3$ (100) surface. Adapted from ref. 37 with modifications.



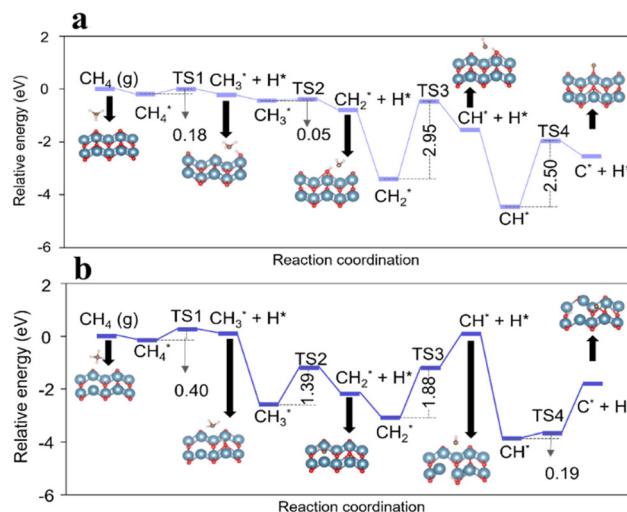


Fig. 5 The energy profiles for the C–H activation on the (a) pristine CaO (111) surface and (b) CaO (111) surface with oxygen vacancy sites. The blue, red, brown, and white balls represent Ca, O, C, and H atoms, respectively. Adapted from ref. 40 with modifications.

coated with graphene. To elucidate this mechanism, the interaction between the formed graphene layer and the underlying CaO was calculated. It was found that the presence of the surface graphene layer destabilizes the oxygen atoms in CaO and induces the further transfer of oxygen to the outer surface of the graphene layer. Following this oxygen transfer process, CH_4 molecules preferentially bind to the acquired oxygen, generating CH_3OH *via* the reaction, which is further decomposed at CVD temperatures to produce CO. Additionally, the calculation results indicate that the energy required for oxygen transfer on the stepped CaO (110) surface is significantly lower than that on the MgO (110) surface, highlighting a unique oxygen desorption pathway specific to CaO. Following oxygen desorption from the graphene coated CaO surface, the CaO structure undergoes rearranges itself, restricting further oxygen desorption from neighbouring sites. Consequently, CO emissions cease experimentally after a certain period.

3.3. Silicon Dioxide (SiO_2)

Although Al_2O_3 , MgO , and CaO exhibit excellent catalytic performance for graphene formation, these templates face challenges in forming complex nanostructures. In contrast, SiO_2 is considered one of the most ideal ceramic oxide candidates for nanostructure formation, as it can form a diverse range of nanostructures, including monodisperse nanoparticles, core-shell particles, nanofibers, silica aerogels, and mesoporous silica. However, the SiO_2 surface has negligible catalytic activity for graphene formation *via* CH_4 decomposition. Hoshikawa *et al.* found that a modification of SiO_2 surfaces with trimethylsilyl groups (TMS) significantly enhanced their catalysis for CVD using acetylene (C_2H_2) as a carbon source.⁴¹ Based on this finding, trimethylsilyl functionalized micro-spherical porous silica (TMS–MPS) was employed as a core material to convert CH_4 into graphene, thereby synthesizing GMS.⁴²

Furthermore, we analysed the reaction mechanism of CH_4 conversion to graphene on the surface of TMS–MPS.⁴³

Fig. 6 illustrates the scheme of TMS modification on MPS and graphene coating *via* CVD using CH_4 as a carbon source. After replacing the silanol groups ($\text{Si}-\text{OH}$) on the silica surface with TMS groups, the TMS groups are converted to Si radicals and polycyclic aromatic hydrocarbons (PAHs) at 900 °C. The presence of Si radicals substantially enhances carbon deposition and lowers the initial graphene formation temperature from 885 °C on pristine SiO_2 to 720 °C. Carbon deposition on TMS–MPS is five times higher than on MPS at 900 °C, demonstrating the catalytic effect induced by Si radicals. DFT calculations also reveal that Si radicals act as active sites for CH_4 dissociation. Additionally, both experimental and computational results demonstrated Si radicals promote the growth of the second layers even when the SiO_2 surface is already coated with a single graphene layer. Furthermore, unlike Al_2O_3 , MgO and CaO , no CO release was detected on either MPS or TMS–MPS, indicating that oxygen vacancies are not formed in these systems. Thus, it is proposed that the mechanism of CH_4 activation on TMS– SiO_2 is fundamentally different from that of other oxide ceramics discussed above.

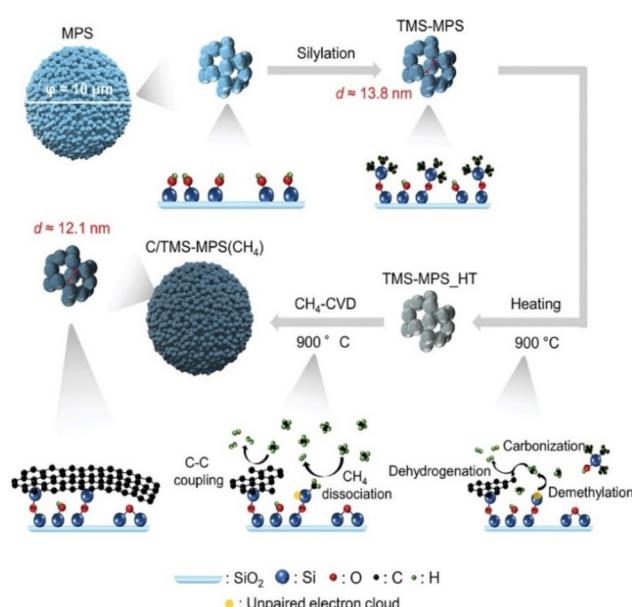


Fig. 6 Trimethylsilylation of the MPS template (top) and modification of the graphene coating process *via* CVD using CH_4 as a precursor (bottom). The φ and d denote the diameter and pore size of samples, respectively.⁴³

Table 1 Comparison of CVD mechanism using CH_4 as a carbon source on different kinds of oxide ceramics

	Induction period	Active sites	CO generation
Al_2O_3 , MgO	Yes	Oxygen vacancies	Yes
CaO	No	Surface oxygen sites	Yes
TMS modified SiO_2	No	Si radicals	No



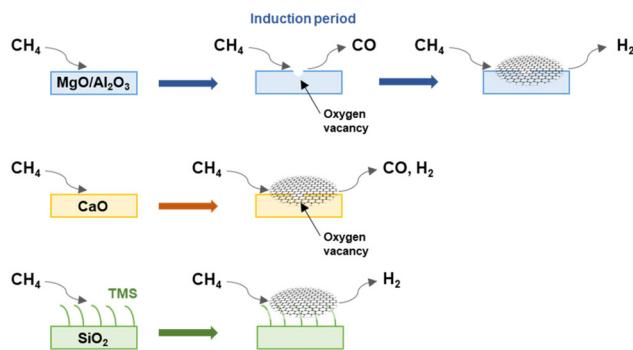


Fig. 7 Graphene formation via CVD using CH_4 as a carbon source on Al_2O_3 , MgO , CaO , and SiO_2 .

4. Conclusions

This minireview has summarized recent progress on the mechanisms of graphene growth on oxide ceramic substrates *via* the chemical vapor deposition process (Table 1 and Fig. 7). Al_2O_3 and MgO facilitate graphene formation through the oxygen vacancy-mediated CH_4 decomposition. During the induction period preceding graphene growth, CH_4 extracts oxygen from the substrate, releasing CO and generating oxygen vacancies as active sites *in situ*. In contrast, CaO supports spontaneous graphene growth without an induction period, accompanied by the release of a significant amount of CO through the unique oxygen transfer mechanism. Meanwhile, pristine SiO_2 lacks activity for methane conversion; however, surface modification with trimethylsilyl groups generates Si radicals *in situ* during heat treatment, which promote CH_4 activation and enable graphene growth. In conclusion, these findings emphasize that activation mechanisms vary significantly depending on the substrate material, even when using the same CH_4 as a carbon source, highlighting the importance of selecting an appropriate system based on the intended application.

From the perspective of templates for graphene synthesis, oxide ceramics are characterized by their nanostructure-forming capabilities and high thermal stability, making them particularly valuable for fabricating three-dimensional graphene, which holds the potential to play a crucial role in fields such as electronics, energy, and biotechnology. Investigating the distinct CVD mechanisms across various templates expands the library of viable candidates and enables precise control over domain size and defect density of 3D graphene, which are key parameters for tuning material performance. It also opens new possibilities for synthesis on unconventional substrates and under non-standard conditions, thereby broadening the potential applications of graphene-based materials.

In addition, it is worth noting that the CVD process using CH_4 offers inherent sustainability advantages. The core reaction ($\text{CH}_4 \rightarrow \text{C} + 2\text{H}_2$) not only provides carbon for graphene formation but also generates hydrogen that can be classified as turquoise hydrogen. This enables efficient utilization of CH_4 in terms of resource efficiency and carbon footprint,

further reinforcing the appeal of CVD approach as a green synthetic platform.

Looking ahead, the discovery of new template materials, as well as innovations in carbon sources and deposition techniques, is expected to drive further advancements in 3D graphene synthesis. Consequently, elucidating the fundamental mechanisms of graphene growth, including carbon nucleation and crystallization processes, will continue to be a critical research focus. We hope that this minireview will serve as a foundation for further advancements in this field.

Author contributions

Writing – original draft: H. Z.; Writing – review & editing: M. Z., T. Y., D. D. T., H. N.

Data availability

No primary research results, software or code have been included and no new data were generated or analysed as part of this review.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by JSPS KAKENHI Grant No. 23H00227; JST A-STEP Grant No. JPMJTR22T6; JST CREST Grant No. JPMJCR24S6; Council for Science, Technology and Innovation (CSTI), Cross-ministerial Strategic Innovation Promotion Program (SIP), the 3rd period of SIP “Creating a materials innovation ecosystem for industrialization” Grant No. JPJ012307 (Funding agency: NIMS); Kondo Memorial Foundation Grant No. 2023-01; “Crossover Alliance to Create the Future with People, Intelligence and Materials” from MEXT, Japan; the Cooperative Research Program of “NJR Mater. & Dev.”; UK’s Royal Society International Exchanges Cost Share (IEC|R3\193106).

References

- 1 K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, Y. Zhang, S. V. Dubonos, I. V. Grigorieva and A. A. Firsov, *Science*, 2004, **306**, 666–669.
- 2 S. V. Morozov, K. S. Novoselov, M. I. Katsnelson, F. Schedin, D. C. Elias, J. A. Jaszczak and A. K. Geim, *Phys. Rev. Lett.*, 2008, **100**, 016602.
- 3 H. Nishihara and T. Kyotani, *Chem. Commun.*, 2018, **54**, 5648–5673.



4 N. Wang, M. K. Samani, H. Li, L. Dong, Z. Zhang, P. Su, S. Chen, J. Chen, S. Huang, G. Yuan, X. Xu, B. Li, K. Leifer, L. Ye and J. Liu, *Small*, 2018, **14**, 1801346.

5 Y. Bai, T. Xu and X. Zhang, *Micromachines*, 2020, **11**, 60.

6 P. Li, C. Chen, J. Zhang, S. Li, B. Sun and Q. Bao, *Front. Mater.*, 2014, **1**, 26.

7 Q. Xiang, J. Yu and M. Jaroniec, *Chem. Soc. Rev.*, 2012, **41**, 782–796.

8 H. W. Kroto, J. R. Heath, S. C. O'Brien, R. F. Curl and R. E. Smalley, *Nature*, 1985, **318**, 162–163.

9 S. Iijima, *Nature*, 1991, **354**, 56–58.

10 S. Iijima and T. Ichihashi, *Nature*, 1993, **363**, 603–605.

11 A. L. Mackay and H. Terrones, *Nature*, 1991, **352**, 762–762.

12 T. Lenosky, X. Gonze, M. Teter and V. Elser, *Nature*, 1992, **355**, 333–335.

13 H. Nishihara, T. Simura, S. Kobayashi, K. Nomura, R. Berenguer, M. Ito, M. Uchimura, H. Iden, K. Arihara, A. Ohma, Y. Hayasaka and T. Kyotani, *Adv. Funct. Mater.*, 2016, **26**, 6418–6427.

14 K. Nomura, H. Nishihara, N. Kobayashi, T. Asada and T. Kyotani, *Energy Environ. Sci.*, 2019, **12**, 1542–1549.

15 W. Yu, Z. Shen, T. Yoshii, S. Iwamura, M. Ono, S. Matsuda, M. Aoki, T. Kondo, S. R. Mukai, S. Nakanishi and H. Nishihara, *Adv. Energy Mater.*, 2024, **14**, 2303055.

16 K. Nomura, H. Nishihara, M. Yamamoto, A. Gabe, M. Ito, M. Uchimura, Y. Nishina, H. Tanaka, M. T. Miyahara and T. Kyotani, *Nat. Commun.*, 2019, **10**, 2559.

17 T. Yoshii, D. Umemoto, M. Yamamoto, Y. Kuwahara, H. Nishihara, K. Mori, T. Kyotani and H. Yamashita, *ChemCatChem*, 2020, **12**, 5834–5834.

18 A. Ohma, Y. Furuya, T. Mashio, M. Ito, K. Nomura, T. Nagao, H. Nishihara, H. Jinnai and T. Kyotani, *Electrochim. Acta*, 2021, **370**, 137705.

19 H. C. Schniepp, J.-L. Li, M. J. McAllister, H. Sai, M. Herrera-Alonso, D. H. Adamson, R. K. Prud'homme, R. Car, D. A. Saville and I. A. Aksay, *J. Phys. Chem. B*, 2006, **110**, 8535–8539.

20 G. Eda, G. Fanchini and M. Chhowalla, *Nat. Nanotechnol.*, 2008, **3**, 270–274.

21 W. Strupinski, K. Grodecki, A. Wysmolek, R. Stepniewski, T. Szkopek, P. E. Gaskell, A. Grüneis, D. Haberer, R. Bozek, J. Krupka and J. M. Baranowski, *Nano Lett.*, 2011, **11**, 1786–1791.

22 A. N. Obraztsov, *Nat. Nanotechnol.*, 2009, **4**, 212–213.

23 Z. Ma, T. Kyotani and A. Tomita, *Chem. Commun.*, 2000, 2365–2366, DOI: [10.1039/B006295M](https://doi.org/10.1039/B006295M).

24 T. Kyotani, *Bull. Chem. Soc. Jpn.*, 2006, **79**, 1322–1337.

25 H. Nishihara, H. Fujimoto, H. Itoi, K. Nomura, H. Tanaka, M. T. Miyahara, P. A. Bonnaud, R. Miura, A. Suzuki, N. Miyamoto, N. Hatakeyama, A. Miyamoto, K. Ikeda, T. Otomo and T. Kyotani, *Carbon*, 2018, **129**, 854–862.

26 T. Kyotani, L.-F. Tsai and A. Tomita, *Chem. Mater.*, 1995, **7**, 1427–1428.

27 T. Kyotani, T. Nagai, S. Inoue and A. Tomita, *Chem. Mater.*, 1997, **9**, 609–615.

28 H. Nishihara, Q.-H. Yang, P.-X. Hou, M. Unno, S. Yamauchi, R. Saito, J. I. Paredes, A. Martínez-Alonso, J. M. D. Tascón, Y. Sato, M. Terauchi and T. Kyotani, *Carbon*, 2009, **47**, 1220–1230.

29 T. Xia, T. Yoshii, K. Nomura, K. Wakabayashi, Z.-Z. Pan, T. Ishii, H. Tanaka, T. Mashio, J. Miyawaki, T. Otomo, K. Ikeda, Y. Sato, M. Terauchi, T. Kyotani and H. Nishihara, *Chem. Sci.*, 2023, **14**, 8448–8457.

30 W. Yu, T. Yoshii, A. Aziz, R. Tang, Z.-Z. Pan, K. Inoue, M. Kotani, H. Tanaka, E. Scholtzová, D. Tunega, Y. Nishina, K. Nishioka, S. Nakanishi, Y. Zhou, O. Terasaki and H. Nishihara, *Adv. Sci.*, 2023, **10**, 2300268.

31 K. Pirabul, Z.-Z. Pan and H. Nishihara, *Front. Mater.*, 2024, **10**, 1345592.

32 X. Cai, Q. Yang, Y. Jin, Z. Tang, X. Gong, J. Shen and B. Hu, *Chem. Commun.*, 2022, **58**, 12483–12486.

33 S. Sunahiro, K. Nomura, S. Goto, K. Kanamaru, R. Tang, M. Yamamoto, T. Yoshii, J. N. Kondo, Q. Zhao, A. Ghulam Nabi, R. Crespo-Otero, D. Di Tommaso, T. Kyotani and H. Nishihara, *J. Mater. Chem. A*, 2021, **9**, 14296–14308.

34 A. Holmen, O. A. Rokstad and A. Solbakken, *Ind. Eng. Chem. Process Des. Dev.*, 1976, **15**, 439–444.

35 N. Muradov, F. Smith and A. T-Raissi, *Catal. Today*, 2005, **102–103**, 225–233.

36 M. Yamamoto, S. Goto, R. Tang, K. Nomura, Y. Hayasaka, Y. Yoshioka, M. Ito, M. Morooka, H. Nishihara and T. Kyotani, *ACS Appl. Mater. Interfaces*, 2021, **13**, 38613–38622.

37 Q. Zhao, M. Yamamoto, K. Yamazaki, H. Nishihara, R. Crespo-Otero and D. Di Tommaso, *Phys. Chem. Chem. Phys.*, 2022, **24**, 23357–23366.

38 Q. Zhao, H. Nishihara, R. Crespo-Otero and D. Di Tommaso, *ACS Appl. Mater. Interfaces*, 2024, **16**, 53231–53241.

39 S. Sunahiro, K. Pirabul, Z. Pan, T. Yoshii, Y. Hayasaka, Q. Zhao, R. Crespo-Otero, D. Di Tommaso, T. Kyotani and H. Nishihara, *Catal. Today*, 2024, **437**, 114763.

40 K. Pirabul, Q. Zhao, S. Sunahiro, Z.-Z. Pan, T. Yoshii, Y. Hayasaka, E. Hoi-Sing Pang, R. Crespo-Otero, D. Di Tommaso, T. Kyotani and H. Nishihara, *Green Chem.*, 2024, **26**, 6051–6062.

41 Y. Hoshikawa, A. Castro-Muñiz, H. Komiyama, T. Ishii, T. Yokoyama, H. Nanbu and T. Kyotani, *Carbon*, 2014, **67**, 156–167.

42 K. Pirabul, Z.-Z. Pan, K. Kanamaru, Y. Horiguchi, Y. Takahashi, A. Kumatai and H. Nishihara, *Carbon*, 2024, **228**, 119376.

43 K. Pirabul, Q. Zhao, Z.-Z. Pan, H. Liu, M. Itoh, K. Izawa, M. Kawai, R. Crespo-Otero, D. Di Tommaso and H. Nishihara, *Small*, 2024, **20**, 2306325.

