

Chemical Science

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: C. He, E. Zhu, W. Liu, Y. Zhu and C. Chen, *Chem. Sci.*, 2026, DOI: 10.1039/D5SC08299D.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

Directing Robust Built-in Electric Fields via Imine Linkage Orientation in COFs for Efficient Dehydrogenative Organic Transformation Coupled with H₂O₂ Photosynthesis

Chang He,^{a, b, †} Weixu Liu,^{b, †} Enwei Zhu,^{a, *} Yongfa Zhu,^{b, *} and Chen Chen^{b, *}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

The built-in electric field (IEF) could be improved via developing donor-acceptor (D-A) type COF photocatalysts, yet available modulation strategies remain limited and poor. Here, we design a series of D-A COFs with isomeric imine linkage to promote the IEF and redox activity. The orientation of imine linkages on D/A centers could effectively adjust dipole moment of COFs, which is increased by ~50%, thereby enhancing the IEF. The charge separation efficiency is also elevated through the enhancement of IEF, leading to exciton binding energy reduced by ~30% and charge-separated state lifetime prolonged by 7-fold. Accordingly, the optimal COF exhibits impressive photocatalytic redox activities (5-fold promoted), achieving a remarkable tetrahydroquinoline dehydrogenation rate of 10.02 mmol/g/h, far exceeding reported metal-free photocatalysts and even comparative with metal photocatalysts, along with a H₂O₂ production rate over 20.01 mmol/g/h. Our findings establish a universal strategy to modulate the IEF which contributes to designing high-performance COF photocatalysts.

Introduction

To address the energy and environmental crises, directly converting solar energy into chemical energy through photocatalysis is a promising strategy for achieving sustainable development.¹⁻³ However, efficient and stable semiconductor photocatalysts are still lacking.⁴⁻⁶ In recent years, two-dimensional (2D) COFs, featuring porous crystalline structures formed through various types of reversible dynamic covalent bonds linking organic functional units, have attracted much attention.⁷⁻⁹ This resultant architecture in COFs is unique, with π -functional units in-plane periodically linked into 2D polymeric conjugated backbones, and the layer frameworks further noncovalently stacked to form separated columnar π -arrays. Such ordered crystalline structures with channels are ideal semiconductor photocatalysts, particularly in overcoming the limitations of light absorption and active sites found in inorganic semiconductors, which show great potential in photocatalysis.^{8,10-15} Nevertheless, their inefficient photogenerated charge separation severely limits their practical application.¹⁶⁻¹⁸ Rational design of 2D COFs via molecular engineering is still a major challenge.

Although researchers have explored a diverse array of molecular engineering strategies to enhance the photocatalytic performance of imine-based COFs—such as fine-tuning the

dipole moment and creating active sites through the introduction of functional groups¹⁹⁻²¹, controlling the interlayer dihedral angle via steric hindrance groups to optimize charge carrier dynamics²²⁻²⁴ and so on, donor-acceptor (D-A) design strategy has been widely demonstrated as one of the most effective and universal approaches, primarily due to its unparalleled ability to generate a robust IEF that dramatically enhances charge separation efficiency¹⁵⁻³¹. 2D D-A COFs feature that the D and A units are alternately arranged in-plane and spatially stacked into dual-continuous π -structures with ordered layer arrays.³² This unique alternating D-A conjugation architecture contributes to numerous super-heterojunctions, which are helpful in promoting the IEF to generate long-lived charge-separated state for photocatalysis.^{33,34} However, strategies for modulating IEF in 2D D-A COFs are predominantly confined to molecular-level optimization of donor and acceptor units, while the repertoire of available modulation approaches remains substantially constrained. The linkages in 2D D-A COFs play a crucial role in optical absorption and electronic property, yet the orientation of the D and A groups relative to the COF linkage has been rarely investigated. It can be predicted that the aforementioned orientation is crucial, given that both the D-A system and the linkage are oriented. The proper orientation, as has been recently demonstrated in electrochemiluminescence,³⁵ will effectively superimpose the effects of both.

Based on the above consideration, a series of 2D D-A COFs featuring spatially separated D/A centers with isomeric imine linkage is rationally designed and successfully synthesized (Scheme 1). The influence of the imine linkage on photocatalytic activity was explored by varying the spatial arrangement of the D/A centers relative to the imine linkage. We reveal that under the same D-A center frameworks, COFs with the imine-linkage

^a Key Laboratory of Preparation and Applications of Environmental Friendly Materials, Jilin Normal University, Changchun, China

^b Engineering Research Center of Advanced Rare Earth Materials, Department of Chemistry, Tsinghua University, Beijing, China


[†] These authors contributed equally to this work.

* Email: zhuenwei05@126.com, zhuyf@tsinghua.edu.cn,

cchen@mail.tsinghua.edu.cn.

Supplementary Information available: See DOI: 10.1039/x0xx00000x



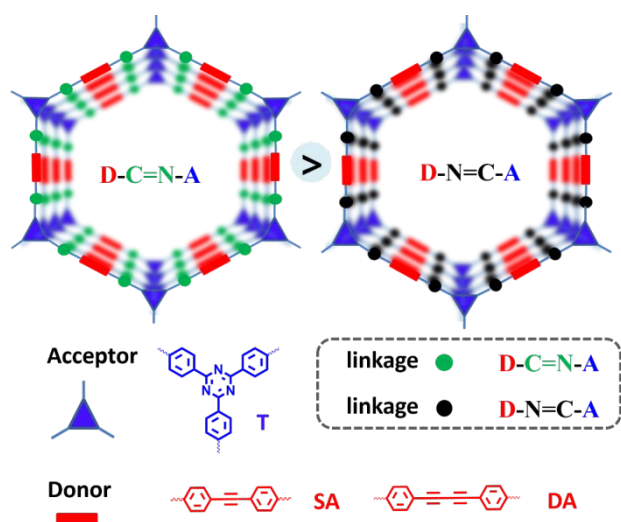

Scheme 1. The as-synthesized D-A COFs with isomeric imine linkage.

nitrogen adjacent to the A center (DCNA) exhibited better activity on the dehydrogenation oxidation of tetrahydroquinoline and the production of hydrogen peroxide (H_2O_2) compared to COFs with the imine-linkage nitrogen adjacent to the D center (DNCA). The structure-activity relationship was further investigated using a range of *in situ*/quasi-*in situ* tests and DFT calculations. The results indicate that COFs with DCNA orientation exhibit the enhanced charge separation efficiency. This can be attributed to a larger overall dipole moment generated from the alignment between the inherent dipole moments of the D-A centers and the polar imine linkage, which is increased by $\sim 50\%$, further establishing a more

robust IEF with more prolonged charge-separated state lifetimes and lower E_b (reduced by $\sim 30\%$). This work highlights the significance of linkage orientation on photocatalytic activity and provide a general strategy for designing high-performance COF photocatalysts.

Results and discussion

Structure confirmation of D-A COFs with isomeric imine linkage

Herein, a series of COFs with the D/A centers spatially arranged oppositely to the imine linkage, were constructed through an acid-catalyzed Schiff base reaction. Specifically, SA-DCNA and DA-DCNA were synthesized by the condensation of acetylenic aldehyde D units and triazine amine A units to form the COFs with DCNA. SA-DNCA and DA-DNCA with DNCA structure were synthesized by the condensation of acetylenic amine D units and triazine aldehyde A units. The structures of SA-DCNA, SA-DNCA, DA-DCNA, and DA-DNCA were confirmed through ^{13}C solid-state nuclear magnetic resonance (^{13}C -ssNMR) spectra, Fourier-transform infrared (FT-IR) spectra, element analysis (EA), thermogravimetric analyses (TGA), powder X-ray diffraction (PXRD), transmission electron microscope (TEM), BET surface area and structural simulation. ^{13}C -ssNMR (Fig. 1a and 1b) shows that the carbon of the imine linkage in SA-DCNA and DA-DCNA exhibit broad peaks at 153 ppm, whereas in SA-DNCA and DA-DNCA, they appear at 155 ppm and 160 ppm, indicating the formation of imine linkage. Meanwhile, the variation in chemical shift is consistent with the change induced by the orientation of the imine linkage. The appearance of FT-IR signal at $\sim 1623\text{ cm}^{-1}$ for $-\text{C}=\text{N}-$ and the disappearance of the $-\text{CH}=\text{O}$ stretching signal at $\sim 1670\text{ cm}^{-1}$ also confirms the condensation of aldehyde and amine groups of organic units (Fig. S1).^{36,37} Additionally, the EA results (Table S1) for C, N, and H in COFs are in well agreement with the theoretical predictions, further verifying the successful synthesis of the four COFs.

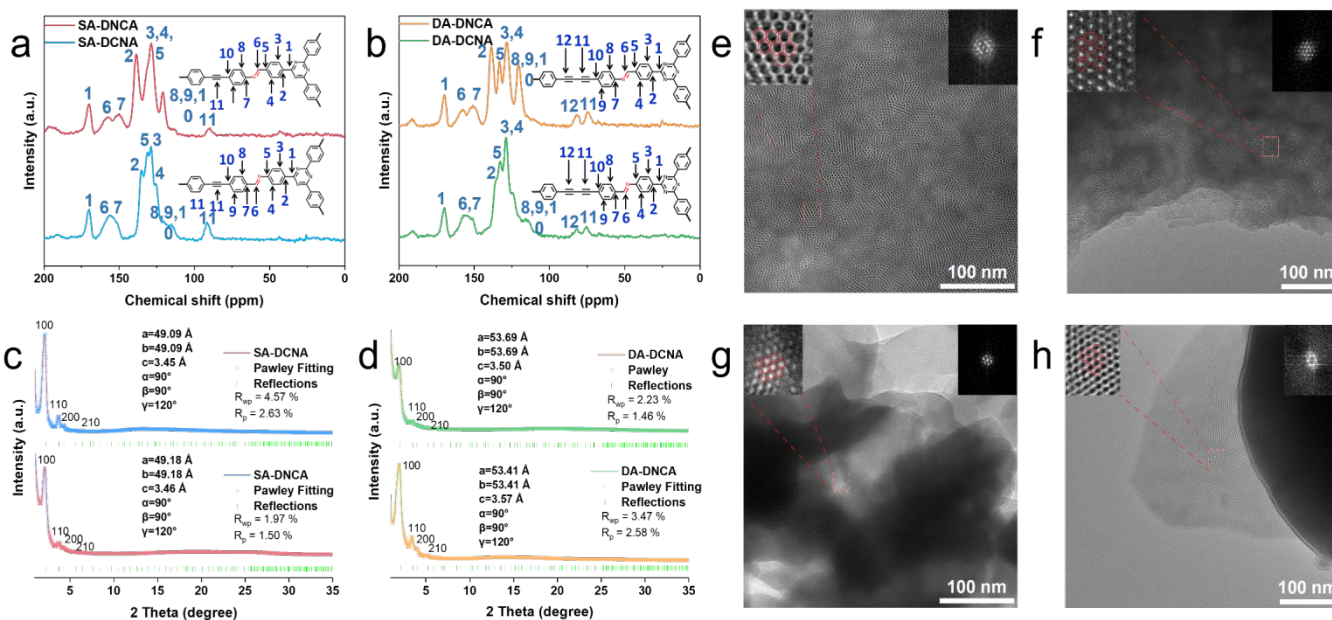


Figure 1. a,b) ^{13}C ssNMR spectra of SA-DCNA and SA-DNCA, DA-DCNA and DA-DNCA. c,d) Experimental and simulated PXRD patterns of SA-DCNA and SA-DNCA, DA-DCNA and DA-DNCA. e-h) TEM images of SA-DCNA, SA-DNCA, DA-DCNA, and DA-DNCA. Left inset: enlarged image of the region within the red dotted box. Right inset: corresponding SAED pattern of the region within the red dotted box.



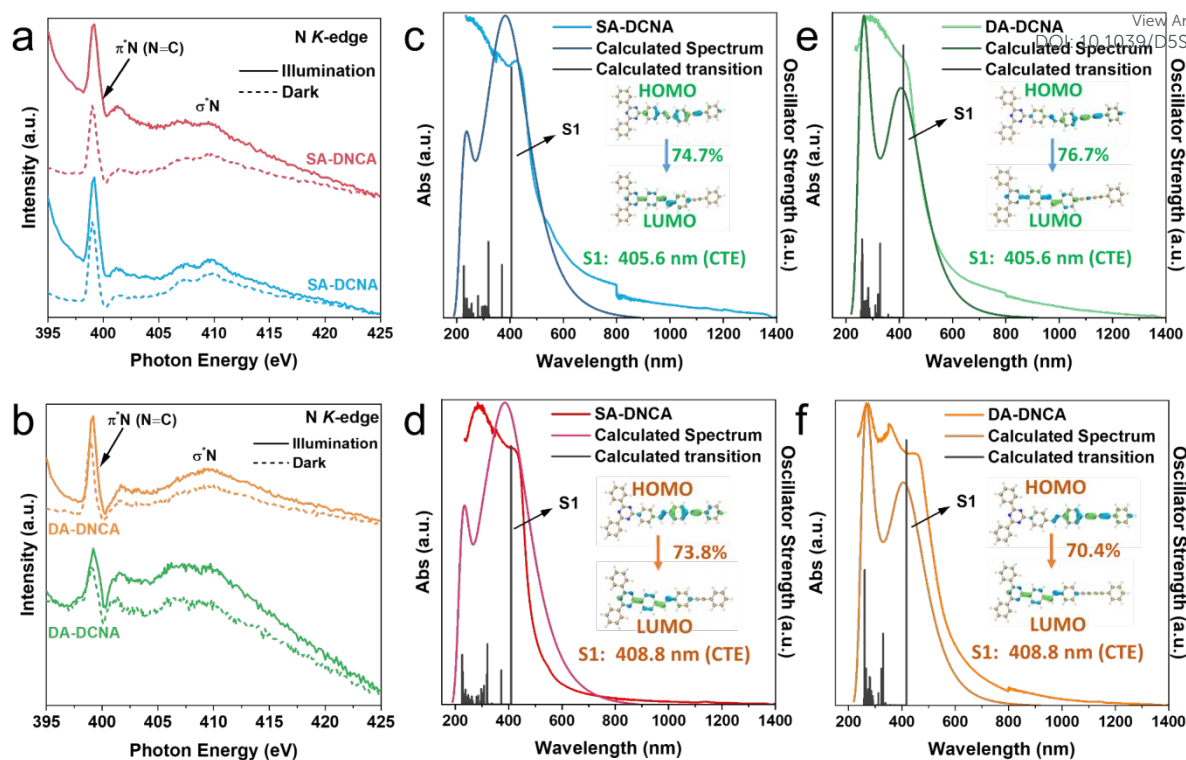


Figure 2. a,b) *In situ* irradiated (405 nm) N K-edge XANES spectra of SA-DCNA and SA-DNCA, DA-DCNA and DA-DNCA. c-f) Comparison of theoretical and experimental DRS spectra for SA-DCNA, SA-DNCA, DA-DCNA, and DA-DNCA.

The crystal structures of COFs are determined by PXRD and structural simulations (Fig. S2–S5). Pawley refinement indicates that the differences between the simulated and experimental PXRD patterns are negligible and all COFs are eclipsed AA-stacking. As shown in Fig. 1c, SA-DCNA and SA-DNCA exhibit identical 2θ peaks at 2.1° , 3.4° , 4.2° , and 6.2° , corresponding to the (100), (110), (200), and (210) planes, respectively, due to the same D-A periodic frameworks. Similarly, DA-DCNA and DA-DNCA also present the same 2θ peaks at 1.9° , 3.4° , 4.0° and 5.2° , which are assigned to the (100), (110), (200) and (210) planes, respectively (Fig. 1d). Therefore, the as-synthesized COFs display 2D hexagonal structures with conjugation backbones extended over the *x-y* plane, as well as forming organized columnar π arrays stacked along the *z* direction. From the TEM images (Fig. 1e–h, S6–S9), the periodically ordered channels in the four COFs are observable, further proving the formation of the 2D topology. The porosities of COFs were also evaluated by nitrogen adsorption experiments at 77 K and the pore diameter ranging from 3.6 nm to 4.1 nm (Fig. S10 and S11). As shown in Fig. S12, scanning electron microscopy (SEM) images reveal a nanocrystalline block morphology. The structural stability of COFs was investigated with TGA (Fig. S13), exhibiting decomposition temperatures above 400 °C under N_2 atmosphere.

The D-A system was confirmed by *in situ* X-ray absorption near edge structure (XANES) spectra, stimulated and measured diffuse reflectance spectra (DRS), and the DFT calculation. The peak around ~ 289.0 eV, associated with the $1s$ to π^* excitation of C atoms in the triazine rings, shows enhanced absorption after irradiation (Fig. S14). Meanwhile, significant increase is also observed in the N K-edge absorption spectrum at ~ 399.0 eV, which is attributed to the $1s$ to π^* excitation of triazine rings (Fig. 2a and 2b).³⁸ This phenomenon is due

to that photogenerated electrons transfer to the triazine-containing structure. Accordingly, the absorption peak corresponding to the $1s$ to π^* excitation of C=C bond at ~ 286.0 eV slightly decreases. It reveals that photogenerated electrons tend to concentrate in the triazine-containing acceptor moieties, whereas the holes stay at alkyne-containing donor moieties, thus confirming the formation of the D-A system within COFs. Meanwhile, charge transfer absorption peaks are observed in the DRS spectra (Fig. S15), further demonstrating the internal charge transfer processes.³⁹ The DRS of four COFs were also simulated (Fig. 2c–f), showing that the excitation of $S_0 \rightarrow S_1$ was dominated by charge transfer excitation (CTE) of $\pi-\pi^*$ from SA/DA-based unit to triazine-based unit. Additionally, the HOMO and LUMO distribution of COFs features D-A characteristics (inset of Fig. 2c–f and S16), where the HOMO is distributed mainly on SA/DA-based unit, and the LUMO is distributed mainly on triazine-based unit. These findings validate the D-A system of as-prepared COFs, allowing the COFs to generate charge-separated states, where the holes remain on the D centers, while the electrons migrate to the A centers.

Manipulating imine linkage orientation to direct robust IEFs

The distribution of localized charge density can significantly affect the dipole moment of the molecule.^{27,40–43} Likewise, polarity alterations arising from the orientation of imine linkages may remarkably modulate the overall dipole moment of COFs. Thus, surface electrostatic potential distribution and molecular dipole moment of four COFs were investigated. It was found that SA-DCNA and DA-DCNA can produce larger dipoles than SA-DNCA and DA-DNCA, respectively. As shown in the Fig. 3a and 3c, the dipole of SA-DCNA is 1.64 Debye, outperforming that of SA-DNCA with 1.01



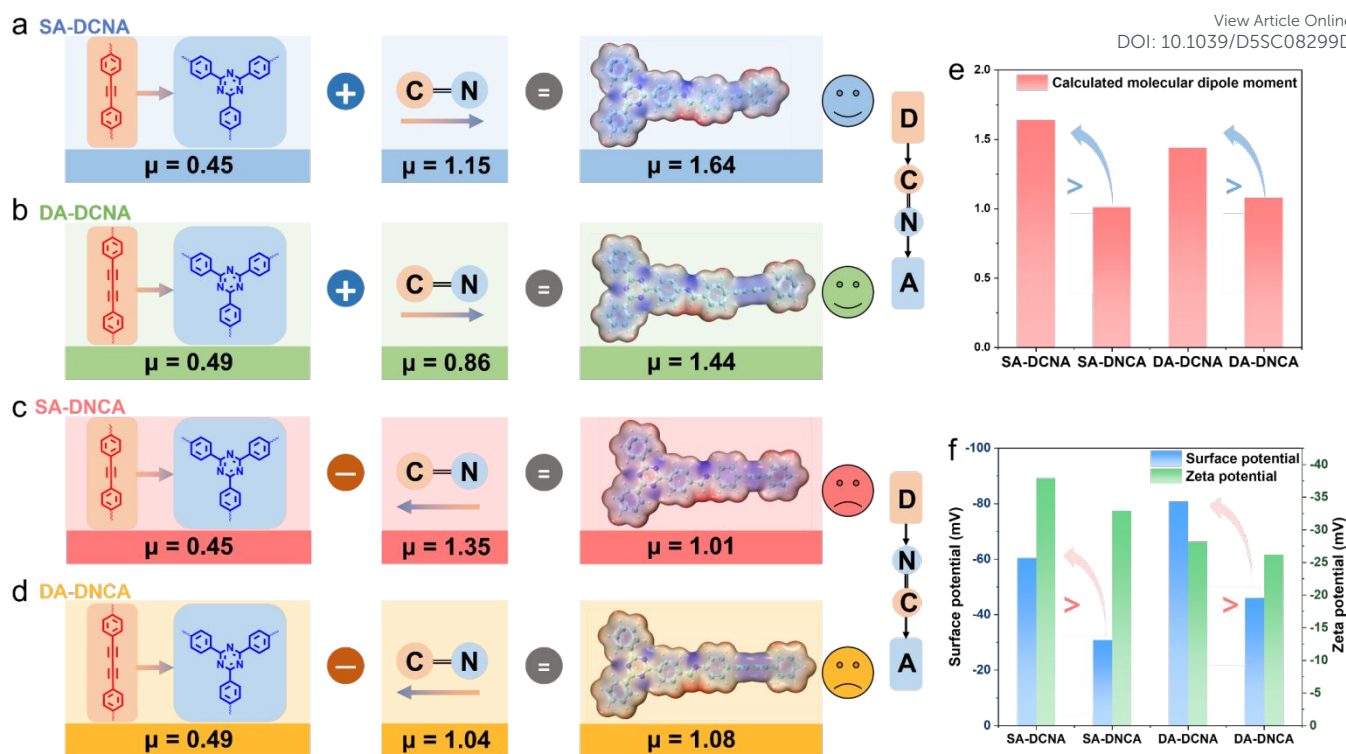



Figure 3. a–d) Surface electrostatic potential distribution and fragment dipole analysis of SA-DCNA, SA-DNCA, DA-DCNA, and DA-DNCA repeating parts. e) Comparison of the dipole moment over COFs. f) Surface potential and Zeta potential of COFs.

Debye. Similarly, DA-DCNA also exceeds DA-DNCA (1.44 Debye > 1.08 Debye, Fig. 3b and 3d). Given that the only difference of SA-DCNA & SA-DNCA and DA-DCNA & DA-DNCA is the orientation of the imine linkage, we quantitatively determined the influence of the imine linkage orientation on the overall molecular dipole via fragment dipole analysis. Specifically, the dipole moments of the D-A segment and the imine linkage within COFs were calculated. It was found that the dipole of the D-A segment is directed from D to A unit, while that of the imine linkage is pointed from the carbon atom to the nitrogen atom, consistent with the classical definition of the dipole moment. According to DFT calculations, the dipole of the D-A segment is 0.45 Debye for both SA-DCNA and SA-DNCA, and the dipole of the imine linkage is 1.15 Debye and 1.35 Debye, respectively. When the dipole of the D-A segment in SA-DCNA aligns with the dipole direction of the imine linkage, a larger cumulative molecular dipole of 1.64 Debye is generated. In contrast, the opposite direction in SA-DNCA produces a dipole of only 1.01 Debye. The modulation of dipoles in DA-DCNA and DA-DNCA by imine linkages is in well agreement with the regulation observed in SA-DCNA and DA-DNCA.

The above analysis indicates that the orientation of the imine linkage can significantly change the polarity of COFs (Fig. 3e). With the intrinsic orientation of imine linkage (C=N) aligning with D-A system, COF would possess a larger overall molecular dipole, which further induces a robust IEF in semiconductors.⁴⁴ Kelvin Probe Force Microscopy (KPFM) and zeta potential tests were conducted to compare the IEF over COFs (Fig. 3f and S17). It is reported that higher surface potential and zeta potential suggest a more robust IEF.^{45–47} We found that the surface potential of SA-DCNA and DA-DCNA is nearly twice as high as that of SA-DNCA and DA-DNCA, with slightly

higher zeta potentials. This indicates that the enhancement of molecular polarity caused by the imine linkage orientation could enable DCNA-type COFs to feature a more robust IEF.

More robust IEFs would facilitate carrier separation more,⁴⁸ which is also confirmed from TAS, TRPL, EPR, XPS and temperature-dependent PL. TAS was performed on four COFs to study the photophysical property in acetonitrile, as shown in Fig. 4a–d. Under 400 nm excitation, all four COFs showed short-lived stimulated emission (SE) signals at the corresponding wavelengths, accompanied with excited-state absorption (ESA) signals in the range of 550–780 nm. Subsequently, the SE signals decayed rapidly, whereas the ESA signals exhibited different decay rates for four COFs, following the trends of SA-DCNA > SA-DNCA and DA-DCNA > DA-DNCA. The TAS spectra are dominated by the ground state bleaching (GSB) absorption band over a longtime scale. It is well known that the long-time-scale GSB signal was observed not only in 2D COFs,^{49,50} but also in 2D carbon materials, which is commonly regarded as charge delocalization in π - π stacking units.^{51–53} Thus, we attribute this GSB to the delocalization of charge carriers within the COFs, indirectly suggesting that the ESA signals in COFs are from charge-separated states. Based on previous studies and the existed D-A systems within these COFs, this ESA signal is ascribed to triazine radical anions.^{49,50} The spectral broadening features of EAS peaks are likely associated with the extended π -conjugation systems of 2D COFs, which is in good agreement with previous reports.⁴⁹ By carrying out kinetic fitting at 650 nm for these COFs, two kinetic components were resolved as shown in Fig. 4e and Table S6. The shorter lifetime component (τ_1) is related to the process of the rapid recombination between holes and triazine radical anions generated



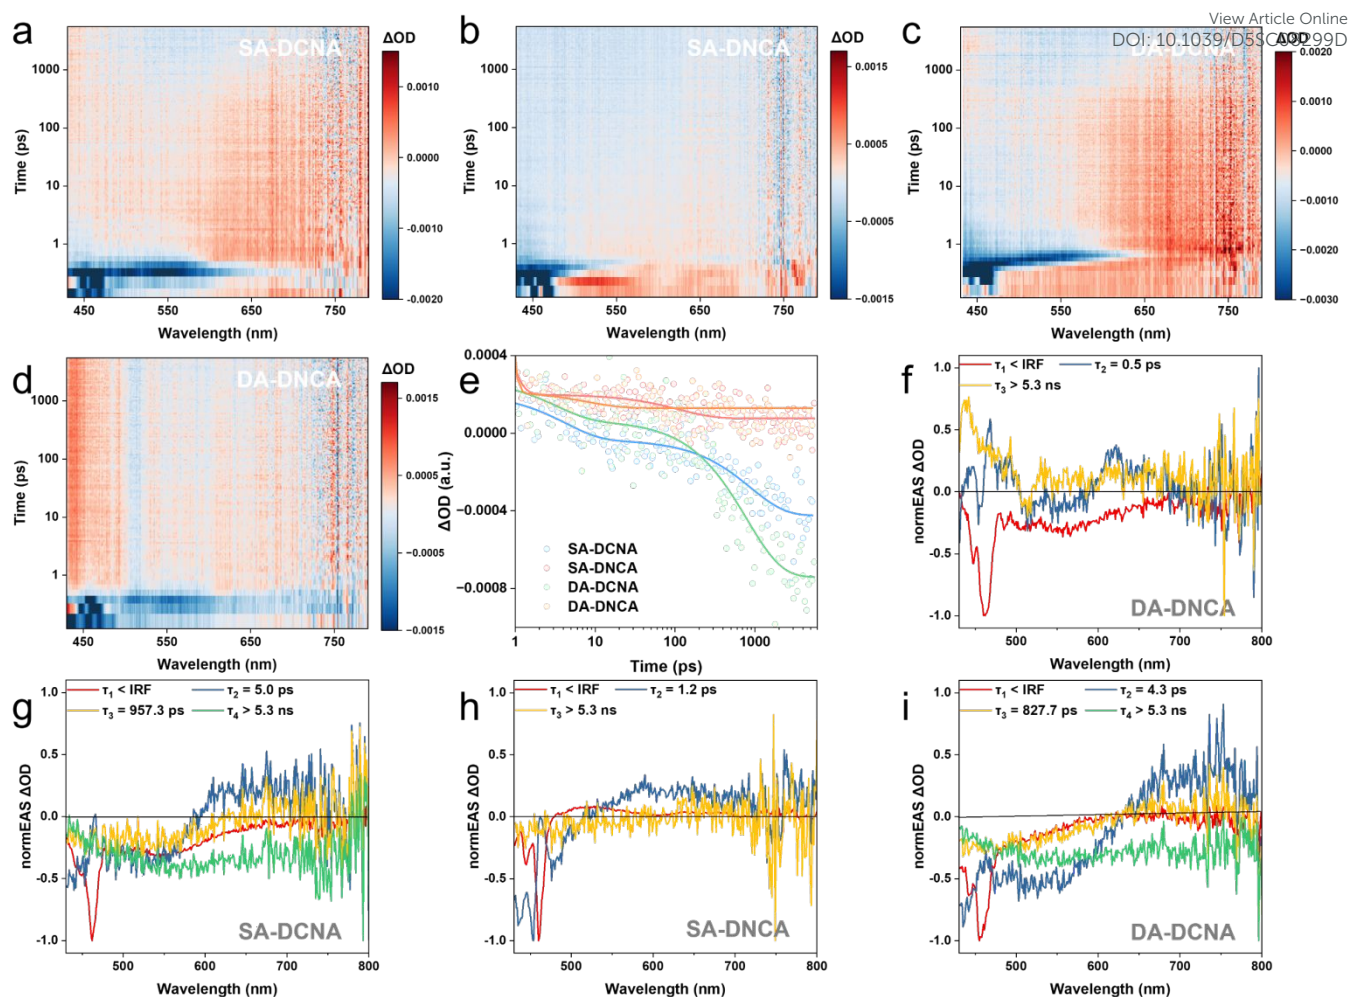


Figure 4. a–d) The femtosecond-transient absorption spectroscopy (fs-TAS) 2D plots of SA-DCNA, SA-DNCA, DA-DCNA, and DA-DNCA. e) Time-absorption profiles of fs-TAS at selected wavelength (650 nm) and the corresponding fitting curves. f–i) Evolution-associated spectra (EAS) of the transient species obtained from global analysis of fs-TAS for SA-DNCA, SA-DCNA, DA-DCNA, and DA-DNCA.

initially from the separated exciton via D-A system. The prolonged lifetime component (τ_2) is attributed to the slow relaxation and recombination process of holes and triazine radical anions after transport and migration. It was found that both τ_1 and τ_2 for four COFs exhibit the trends of SA-DCNA > SA-DNCA and DA-DCNA > DA-DNCA. This indicates that SA-DCNA and DA-DCNA manifest relatively slower electron-hole recombination kinetics, resulting in the formation of prolonged charge-separated species and achieving more effective charge separation.

A more detailed investigation into the photophysical processes within the COFs was conducted using global fitting, as illustrated in Fig. 4f–i. These fs-TAS datasets were best fit to an A→B→C→D→GS (SA-DCNA and DA-DCNA) and A→B→C→GS (SA-DNCA and DA-DNCA) first-order sequential kinetic model, which could also be validated by the well agreement between the fitting curves and the original fs-TAS data at various wavelengths (Fig. S18).

For the EAS spectra resolved from COFs, due to the rapid dissociation of excitons into charge-separated (CS) states in D-A type 2D polymers, typically within the instrument response function (IRF) of fs-TAS,⁴⁹ hence we attribute the ultrafast ESA1 to the exciton state. It is easily seen that these exciton state spectral features are very

similar, especially at < 500 nm, which is due to the fact that their major light-absorbing functional groups are identical. For SA-DCNA and DA-DCNA (Fig. 4g and 4i), the obtained ESA2 and ESA3 resembles with each other, both containing characteristic absorption peaks (~650 nm) of triazine radical anions.^{49,50} We assigned them respectively to the CT and CS1 states. The CT state represents the unrelaxed hot CS1 state,^{54–57} which undergoes 5.0 ps and 4.3 ps relaxation to the CS1 state, respectively. The ESA4 state is the long-time-scale GSB signal mentioned above, and we attribute ESA4 state to the delocalization of triazine radical anions within SA-DCNA and DA-DCNA. Thus the 957.3 ps and 827.7 ps for SA-DCNA and DA-DCNA, respectively, are the processes in which the CS1 state undergoes interlayer charge migration. As for the final evolution, it involves the formation of superoxide radical anions, as well as the recombination or return to the GS of triazine radical anions and holes. Due to the limited time detection range of fs-TAS, accurate time constants of GSB to GS state cannot be obtained here through kinetic fitting.

For the EAS resolved from SA-DNCA and DA-DNCA (Fig. 4f and 4h), the results are slightly different. We did not observe CS states and long-lived GSB signals, where the ESA3 was almost with no features.



Therefore, the CT states generated from exciton dissociation directly

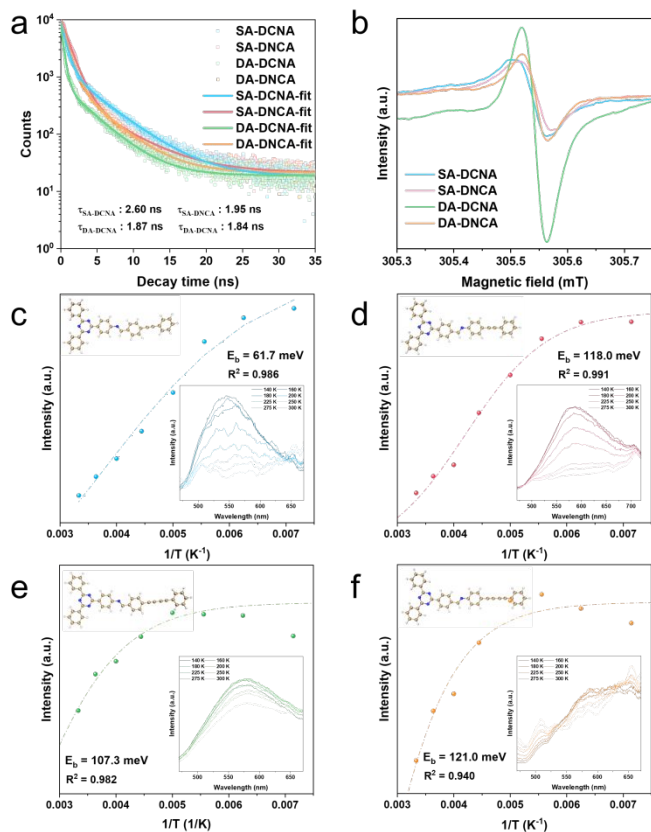


Figure 5. a) Time-dependent photoluminescence (TRPL) spectra and the fitted lifetime of COFs. b) Solid-state electron paramagnetic resonance (EPR) spectra of COF powders. c–f) Temperature-dependent PL spectra from 140 to 300 K under excitation at 420 nm and the fitted exciton binding energy (E_b) of SA-DCNA, SA-DNCA, DA-DCNA, and DA-DNCA.

relax to the GS within 1.2 ps and 0.5 ps, respectively. These short-lived and hot CS states, which are not fully dissociated, are unfavorable for photocatalysis and difficult to participate in the redox reaction, further indicating the role of imine linkage orientation in stabilizing and forming long-lived triazine radical anions.

TRPL measurements were employed to further evaluate the excited-state lifetime of COFs in acetonitrile under 440 nm irradiation. As shown in Fig. 5a and Table S7, the PL kinetic for COFs were determined through bi-exponential fitting, which is consistent with the TAS kinetic. The process with a shorter lifetime (~ 1 ns) is ascribed to the rapid recombination and radiative luminescence of charge carriers, not contributing to the overall photocatalytic process. The process with prolonged lifetime is associated with the slow recombination of charge-separated states, and a larger proportion of slow process is more beneficial for enhancing photocatalytic activity. It is observed that SA-DCNA and DA-DCNA have a higher proportion of slow process relative to SA-DNCA and DA-DNCA, giving rise to longer average lifetimes for SA-DCNA and DA-DCNA. This illustrates that SA-DCNA and DA-DCNA have more robust IEFs, resulting in more effective charge separation, which is also confirmed by TDDFT. The electron, hole, and overlap integral distributions with series of

indexes (Fig. S19 and Table S8) indicate that SA-DCNA and DA-DCNA feature less overlap of electron and hole in excited states compared to those of SA-DNCA and DA-DNCA.

Furthermore, EPR and X-ray photoelectron spectroscopy (XPS) reveal that the orientation of the imine linkage in COFs significantly affects the charge separation within the same D-A system, and COFs with DCNA structure exhibit enhanced charge separation efficiency. As shown in Fig. 5b, under visible light irradiation, all four COFs exhibit a signal at $g = 2.004$, indicating the presence of unpaired electrons in the conduction band.⁵⁸ However, there is a notable difference in EPR intensity, with SA-DCNA and DA-DCNA exhibiting higher intensity compared to SA-DNCA and DA-DNCA, respectively. As for XPS, the peak around ~ 285.7 eV, corresponding to carbon atoms in triazine rings, exhibits a shift toward lower binding energy after irradiation (Fig. S20), which is due to that photogenerated electrons transfer to the triazine-containing structure. And the shift magnitude trends for these four COFs remain consistent with those of EPR, TAS, and TRPL. To quantitatively assess the charge separation efficiency of COFs, temperature-dependent PL were performed to calculate the E_b , as shown in Fig. 5c–f. In temperature-dependent PL spectra, the fluorescence intensity of exciton transitions diminishes as the temperature rises. This is because that excitons are more prone to dissipate energy through non-radiative processes at elevated temperatures, such as vibrational relaxation, instead of fluorescence. The PL intensity of four COFs decreases with the rising temperature, indicating that excitons undergo thermally activated non-radiative recombination processes. The E_b of SA-DCNA, SA-DNCA, DA-DCNA, and DA-DNCA are determined as 61.7 meV, 118.0 meV, 107.3 meV and 121.0 meV, respectively. This illustrates that the alignment of the imine linkage with the D-A direction in COFs reduces E_b and enhances charge separation, which are consistent with the trend obtained in calculated E_b using TDDFT for the repeating units (Table S8). Therefore, COFs with aligned dipole direction of D-A segment and imine linkage generate a larger molecular dipole, resulting in a more robust IEF, which reduces E_b and enhances carrier separation.

Enhancement of photocatalytic redox activity via imine linkage orientation.

The photocatalytic activity over these COFs need to be evaluated to confirm the above results. The dehydrogenation reaction of N-heterocycles could be driven by photogenerated holes and activated oxygen species, such as superoxide radicals and singlet oxygen, resulting in high-value products. This sustainable and mild transformation route not only produces valuable organic compounds but also generates H_2O_2 simultaneously. Hence, the dehydrogenation of tetrahydroquinoline was employed as a model reaction for COFs, which provides a comprehensive assessment of the oxidative and reductive activities of COFs. It is noteworthy that SA-DCNA and DA-DCNA exhibits better activity compared to SA-DNCA and DA-DNCA in different types of solvent (Fig. 6a and S21), which is in accordance with the charge separation analysis. Especially, DA-DCNA with alternated diyne-based D center exhibited the best photocatalytic activity, achieving a remarkable photocatalytic dehydrogenation rate for tetrahydroquinoline of 10.02 mmol $g^{-1} h^{-1}$, along with a hydrogen peroxide production rate of 20.01 mmol $g^{-1} h^{-1}$, which is the top level of metal-free catalytic systems, even surpassing many metal photocatalysts (Fig. 6e and



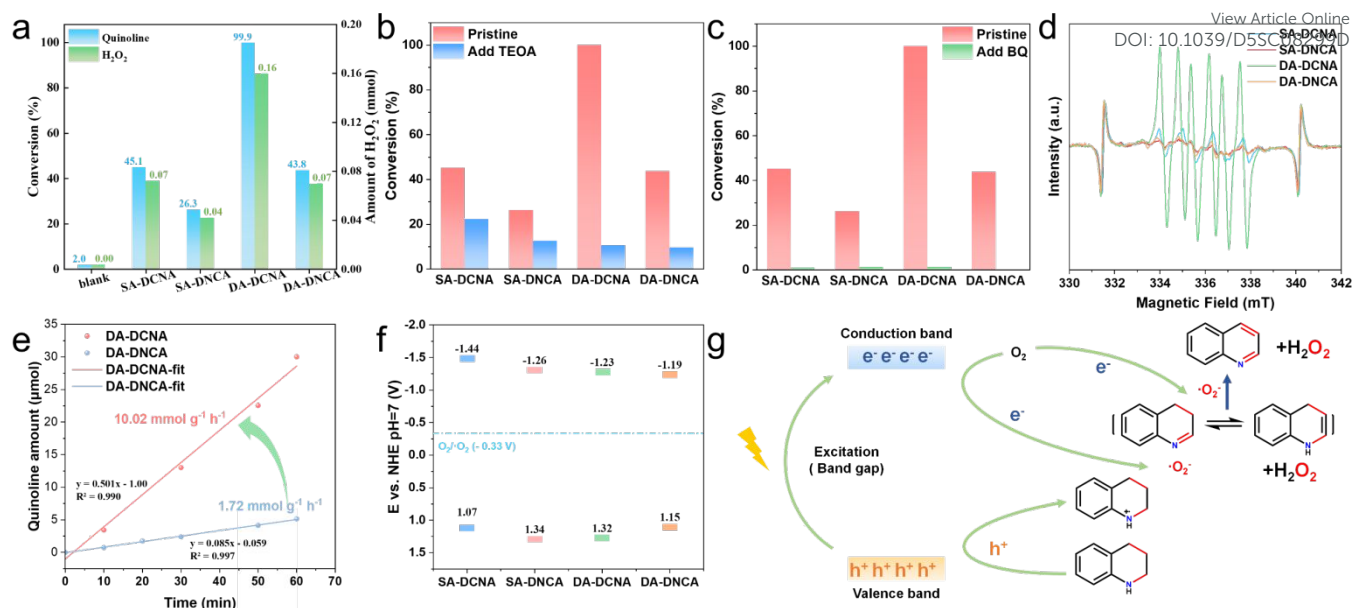


Figure 6. a) Production of quinoline and hydrogen peroxide over COFs. Conditions: 1 atm oxygen, 298 K, 0.1 mmol tetrahydroquinoline, 3 mg catalyst, 5 h, LED light (420 nm). It should be noted that the selectivity is over 99.9% unless otherwise stated. b,c) Quenching experiments for hole and superoxide. d) EPR detection for $\cdot\text{O}_2^-$ under irradiation. e) Dehydrogenation rate comparison over DA-DCNA and DA-DNCA. f) Schematic energy band diagrams of COFs. g) Mechanism diagram of photocatalytic oxidative dehydrogenation coupled with H₂O₂ photosynthesis over COFs.

Table S10). Comparative experiments as well as quenching experiments (Fig. 6b, 6c and Table S9) and *in situ* EPR (Fig. 6d) indicate that $\cdot\text{O}_2^-$ and holes function as the crucial active species to participate in oxygen and tetrahydroquinoline activation. The energy band structure (Fig. 6f) is determined via UV-vis-NIR DRS (for optical band gap, Fig. S15) and ultraviolet photo-electron spectroscopy (UPS, for Fermi level and valence band position, Fig. S22), indicating that COFs can thermodynamically activate oxygen to superoxide radicals. Thus, the mechanism for the photocatalytic reaction is as follows (Fig. 6g). The separation of excitons is due to the D-A system after irradiation. Tetrahydroquinoline molecules nearby are rapidly oxidized by holes on D centers, resulting in the formation of tetrahydroquinoline radical cations. Meanwhile, the electrons at A centers react with dissolved O₂ to generate superoxide radicals, participating in the dehydrogenation of tetrahydroquinoline radical cations, simultaneously producing H₂O₂.

Conclusions

In summary, a universal strategy has been developed that COFs with DCNA configuration exhibit more robust IEF, resulting in a significant enhancement in photocatalytic performance relative to COFs with DNCA. The underlying cause is that the polar imine linkage orientation induces a dramatic change in overall polarity of COFs. With the intrinsic orientation of imine linkage aligning with D-A system, it will result in a larger dipole and form a more robust IEF, significantly improving the carrier separation efficiency of COFs. Consequently, DCNA COFs exhibit more prolonged charge-separated state lifetimes and much lower E_b , obtaining over 5-fold enhancement in photocatalytic oxygen activation compared to DNCA type COFs. This work

demonstrates that the linkage orientation has a remarkable impact on the charge separation and provide a general and transformative guidance for designing high-performance COF photocatalysts.

Author contributions

C.H., W.L., and E.Z. conceived the project. Y.Z. and C.C. guided the research. C.H., W.L., and E.Z. performed experimental work. W.L. performed the computational studies. C.H., W.L., and E.Z. cowrote the manuscript. All authors participated in data analysis.

Conflicts of interest

There are no conflicts to declare.

Data availability

The data supporting this article have been included as part of the Supplementary Information.

Acknowledgements

This work was supported by Beijing Natural Science Foundation(Z250018), National Natural Science Foundation of China (U22B2071, 22136002, U24A20540), Yunnan Provincial Science and Technology Project at Southwest United Graduate School (202302AO370017), National Key Research and Development Project of China (2020YFA0710304) and Special Fund Project of Jiangsu Province for Scientific and Technological Innovation in Carbon Peaking and Carbon Neutrality



(BK20220023). We thank Prof. Wenqing Yao of Analysis Center, Tsinghua University, for her help on XPS/*in situ* XPS/UPS. We thank the 1W1A station at the Beijing Synchrotron Radiation Facility for help in PXRD. We thank the Catalysis and Surface Science End station at the BL11U beamline in the National Synchrotron Radiation Laboratory (NSRL) for help in *in situ* XANES.

References

- Z. Teng, Q. Zhang, H. Yang, K. Kato, W. Yang, Y.-R. Lu, S. Liu, C. Wang, A. Yamakata, C. Su, *Nat. Catal.* **2021**, *4*, 374-384.
- J. Kosco, M. Bidwell, H. Cha, T. Martin, C. T. Howells, M. Sachs, D. H. Anjum, S. Gonzalez Lopez, L. Zou, A. Wadsworth, *Nat. Mater.* **2020**, *19*, 559-565.
- Y. Zhang, C. Pan, G. Bian, J. Xu, Y. Dong, Y. Zhang, Y. Lou, W. Liu, Y. Zhu, *Nat. Energy* **2023**, *8*, 361-371.
- A. M. Evans, L. R. Parent, N. C. Flanders, R. P. Bisbey, E. Vitaku, M. S. Kirschner, R. D. Schaller, L. X. Chen, N. C. Gianneschi, W. R. Dichtel, *Science* **2018**, *361*, 52-57.
- C. Gropp, T. Ma, N. Hanikel, O. M. Yaghi, *Science* **2020**, *370*, eabd6406.
- X. Liu, D. Huang, C. Lai, G. Zeng, L. Qin, H. Wang, H. Yi, B. Li, S. Liu, M. Zhang, *Chem. Soc. Rev.* **2019**, *48*, 5266-5302.
- K. Geng, T. He, R. Liu, S. Dalapati, K. T. Tan, Z. Li, S. Tao, Y. Gong, Q. Jiang, D. Jiang, *Chem. Rev.* **2020**, *120*, 8814-8933.
- M. Wang, M. Ballabio, M. Wang, H.-H. Lin, B. P. Biswal, X. Han, S. Paasch, E. Brunner, P. Liu, M. Chen, *J. Am. Chem. Soc.* **2019**, *141*, 16810-16816.
- R. Chen, Y. Wang, Y. Ma, A. Mal, X.-Y. Gao, L. Gao, L. Qiao, X.-B. Li, L.-Z. Wu, C. Wang, *Nat. Commun.* **2021**, *12*, 1354.
- Y. Zhang, J. Zhang, S. Dou, H. Shang, J. Xu, Y. Dong, Y. Zhang, Y. Lou, C. Pan and Y. Zhu, Unveiling the Role of Excited-State Dipole Moment: Governing Non-Sacrificial H₂O₂ Generation on Porphyrin Photocatalysts, *Angew Chem Int Ed Engl*, 2025, DOI: 10.1002/anie.202512844, e202512844.
- Z. Xue, B. Zhang, Q. Guo, Y. Wang, Q. Li, K. Yang and S. Qiao, Sacrificial-Agent-Triggered Mass Transfer Gating in Covalent Organic Framework for Hydrogen Peroxide Photocatalysis, *Adv Mater*, 2025, *37*, e10201.
- H. Tan, P. Zhou, Y. Gu, Y. Liu, W. Chen, H. Guo, F. Lin, H. Luo, X. Cao, L. Zeng, M. Luo and S. Guo, Separation-free artificial photosynthesis of concentrated hydrogen peroxide and value-added fuels over Ta atomic sites, *Nat Commun*, 2025, *16*, 8784.
- D. Li, C. Li, L. Zhang, H. Li, L. Zhu, D. Yang, Q. Fang, S. Qiu, X. Yao, *J. Am. Chem. Soc.* **2020**, *142*, 8104-8108.
- H. Wang, Y. Yang, X. Yuan, W. L. Teo, Y. Wu, L. Tang, Y. Zhao, *Mater. Today* **2022**, *53*, 106-133.
- C. Kang, K. Yang, Z. Zhang, A. K. Usadi, D. C. Calabro, L. S. Baugh, Y. Wang, J. Jiang, X. Zou, Z. Huang, *Nat. Commun.* **2022**, *13*, 1370.
- M. Wang, S. Fu, P. Petkov, Y. Fu, Z. Zhang, Y. Liu, J. Ma, G. Chen, S. M. Gali, L. Gao, *Nat. Mater.* **2023**, *22*, 880-887.
- T. Ma, E. A. Kapustin, S. X. Yin, L. Liang, Z. Zhou, J. Niu, L.-H. Li, Y. Wang, J. Su, J. Li, *Science* **2018**, *361*, 48-52.
- L. Li, Q. Yun, C. Zhu, G. Sheng, J. Guo, B. Chen, M. Zhao, Z. Zhang, Z. Lai, X. Zhang, *J. Am. Chem. Soc.* **2022**, *144*, 6475-6482.
- Y.-Y. Gu, J. Wang, Q. Tang, H. Wei, J. Ning, X. Lan, X. Wang, X. Li, Y. Jia, S. Wang and L. Hao, Insights into Substituent Effects on the Fundamental Photocatalytic Processes of Covalent Organic Frameworks toward H₂ Evolution and H₂O₂ Production Reactions, *ACS Catalysis*, 2024, *14*, 11262-11272.
- Y. Feng, G. Wang, R. Liu, X. Ye, S. Tao, M. A. Addicoat, Z. Li, Q. Jiang and D. Jiang, Photoresponsive Covalent Organic Frameworks: Visible-Light Controlled Conversion of Porous Structures and Its Impacts, *Angew Chem Int Ed Engl*, 2024, *63*, e202400009.
- F. Ma, T. Gao, X. Sun, C. Han, Y. Wang, A. Jiang, Y. Zhou, G. Liang, H. Wang, L. Wang, B. Jia, Y. Huang, H. Huang, X. Y. Kong, H. Li, N. Huang, T. Ma and L. Ye, Keto-enol tautomerism as dynamic electron/hole traps promote charge carrier separation for hydrogen peroxide photosynthesis, *Nat Commun*, 2025, *16*, 7432.
- X. X. Wang, C. R. Zhang, R. X. Bi, Z. H. Peng, A. M. Song, R. Zhang, H. X. He, J. X. Qi, J. W. Gong, C. P. Niu, R. P. Liang and J. D. Qiu, Reducing the Exciton Binding Energy of Covalent Organic Framework Through π - Bridges to Enhance Photocatalysis, *Advanced Functional Materials*, 2024, *35*.
- L. Zou, Z. A. Chen, D. H. Si, S. L. Yang, W. Q. Gao, K. Wang, Y. B. Huang and R. Cao, Boosting CO₂ Photoreduction via Regulating Charge Transfer Ability in a One-Dimensional Covalent Organic Framework, *Angew Chem Int Ed Engl*, 2023, *62*, e202309820.
- K. Yu, P. He, D. Zhang, H. Wu, K. Shu, H. Long, Y. Sun, X. Pei, B. Jiang, K. Cao, Y. Li and L. Ma, Full - Dimensional Control of Covalent Organic Frameworks Through Repulsion - Torsion Effect: Prominent 1D Above 2D and 3D Structures, *Angew Chem Int Ed Engl*, 2025, *137*.
- Y. Wang, W. Hao, H. Liu, R. Chen, Q. Pan, Z. Li, Y. Zhao, *Nat. Commun.* **2022**, *13*, 100.
- W. Li, X. Huang, T. Zeng, Y. A. Liu, W. Hu, H. Yang, Y. B. Zhang, K. Wen, *Angew. Chem. Int. Ed.* **2021**, *60*, 1869-1874.
- Z. Chen, J. Wang, M. Hao, Y. Xie, X. Liu, H. Yang, G. I. Waterhouse, X. Wang, S. Ma, *Nat. Commun.* **2023**, *14*, 1106.
- Y. Song, A. Li, P. Li, L. He, D. Xu, F. Wu, F. Zhai, Y. Wu, K. Hu, S. Wang, *Chem. Mater.* **2022**, *34*, 2771-2778.
- H. Wang, H. Wang, Z. Wang, L. Tang, G. Zeng, P. Xu, M. Chen, T. Xiong, C. Zhou, X. Li, *Chem. Soc. Rev.* **2020**, *49*, 4135-4165.
- R. Xia, X. Zheng, C. Li, X. Yuan, J. Wang, Z. Xie, X. Jing, *ACS Nano* **2021**, *15*, 7638-7648.
- C. Qin, X. Wu, L. Tang, X. Chen, M. Li, Y. Mou, B. Su, S. Wang, C. Feng, J. Liu, *Nat. Commun.* **2023**, *14*, 5238.
- X. Zhang, K. Geng, D. Jiang, G. D. Scholes, *J. Am. Chem. Soc.* **2022**, *144*, 16423-16432.
- A. M. Evans, A. Giri, V. K. Sangwan, S. Xun, M. Bartnof, C. G. Torres-Castaneda, H. B. Balch, M. S. Rahn, N. P. Bradshaw, E. Vitaku, *Nat. Mater.* **2021**, *20*, 1142-1148.
- Y. Mou, X. Wu, C. Qin, J. Chen, Y. Zhao, L. Jiang, C. Zhang, X. Yuan, E. Huixiang Ang, H. Wang, *Angew. Chem. Int. Ed.* **2023**, *62*, e202309480.
- R. Luo, X. Luo, H. Xu, S. Wan, H. Lv, B. Zou, Y. Wang, T. Liu, C. Wu, Q. Chen, S. Yu, P. Dong, Y. Tian, K. Xi, S. Yuan, X. Wu, H. Ju, J. Lei, *J. Am. Chem. Soc.* **2024**, *146*, 16681-16688.
- J. N. Chang, Q. Li, J. W. Shi, M. Zhang, L. Zhang, S. Li, Y. Chen, S. L. Li, Y. Q. Lan, *Angew. Chem.* **2023**, *135*, e202218868.
- C. Wang, Z. Zhang, Y. Zhu, C. Yang, J. Wu, W. Hu, *Adv. Mater.* **2022**, *34*, 2102290.
- H. Cheng, H. Lv, J. Cheng, L. Wang, X. Wu, H. Xu, *Adv. Mater.* **2022**, *34*, 2107480.
- S. Bi, P. Thiruvengadam, S. Wei, W. Zhang, F. Zhang, L. Gao, J. Xu, D. Wu, J.-S. Chen, F. Zhang, *J. Am. Chem. Soc.* **2020**, *142*, 11893-11900.
- K. Wu, X.-Y. Liu, P.-W. Cheng, Y.-L. Huang, J. Zheng, M. Xie, W. Lu, D. Li, *J. Am. Chem. Soc.* **2023**, *145*, 18931-18938.
- H. Ben, G. Yan, H. Liu, C. Ling, Y. Fan, X. Zhang, *Adv. Funct. Mater.* **2022**, *32*, 2104519.
- J. P. Jeon, Y. J. Kim, S. H. Joo, H. J. Noh, S. K. Kwak, J. B. Baek, *Angew. Chem.* **2023**, *135*, e202217416.
- G. Fu, D. Yang, S. Xu, S. Li, Y. Zhao, H. Yang, D. Wu, P. S. Petkov, Z.-A. Lan, X. Wang, *J. Am. Chem. Soc.* **2024**, *146*, 1318-1325.
- Z. Zhang, Y. Zhu, X. Chen, H. Zhang, J. Wang, *Adv. Mater.* **2019**, *31*, 1806626.



- 45 R. Chen, C. Ni, J. Zhu, F. Fan, C. Li, *Nat. Protoc.* **2024**, 1-33.
- 46 Y. Guo, Q. Zhou, J. Nan, W. Shi, F. Cui, Y. Zhu, *Nat. Commun.* **2022**, *13*, 2067.
- 47 Y. Sheng, W. Li, L. Xu, Y. Zhu, *Adv. Mater.* **2022**, *34*, 2102354.
- 48 R. Chen, S. Pang, H. An, J. Zhu, S. Ye, Y. Gao, F. Fan, C. Li, *Nat. Energy* **2018**, *3*, 655-663.
- 49 S. Jin, X. Ding, X. Feng, M. Supur, K. Furukawa, S. Takahashi, M. Addicoat, M. E. El-Khouly, T. Nakamura, S. Irle, *Angew. Chem. Int. Ed* **2013**, *52*, 2017-2021.
- 50 S. Jin, M. Supur, M. Addicoat, K. Furukawa, L. Chen, T. Nakamura, S. Fukuzumi, S. Irle, D. Jiang, *J. Am. Chem. Soc.* **2015**, *137*, 7817-7827.
- 51 M. A. Herranz, C. Ehli, S. Campidelli, M. Gutiérrez, G. L. Hug, K. Ohkubo, S. Fukuzumi, M. Prato, N. Martín, D. M. Guldi, *J. Am. Chem. Soc.* **2008**, *130*, 66-73.
- 52 M. Ohtani, S. Fukuzumi, *Chem. Commun.* **2009**, 4997-4999.
- 53 J. Malig, N. Jux, D. Kiessling, J. J. Cid, P. Vazquez, T. Torres, D. M. Guldi, *Angew. Chem. Int. Ed.* **2011**, *50*, 3561-3565.
- 54 C. Wang, B. Wu, Y. Li, T. Dong, Y. Chai, Y. Zhang, C. Wang, *Angew. Chem. Int. Ed.* **2023**, *62*, e202300377.
- 55 Y. Chai, L. Liu, Y. Xu, X. Liu, C. Wang, Y. Bo, Y. Zhang, Z. Wang, Y. Weng, D. M. Guldi, *J. Am. Chem. Soc.* **2023**, *145*, 14190-14195.
- 56 J. A. Christensen, B. T. Phelan, S. Chaudhuri, A. Acharya, V. S. Batista, M. R. Wasielewski, *J. Am. Chem. Soc.* **2018**, *140*, 5290-5299.
- 57 T. W. Kim, S. Jun, Y. Ha, R. K. Yadav, A. Kumar, C.-Y. Yoo, I. Oh, H.-K. Lim, J. W. Shin, R. Ryoo, *Nat. Commun.* **2019**, *10*, 1873.
- 58 J. Yang, A. Acharjya, M.-Y. Ye, J. Rabeah, S. Li, Z. Kochovski, S. Youk, J. Roeser, J. Grüneberg, C. Penschke, M. Schwarze, T. Wang, Y. Lu, R. van de Krol, M. Oschatz, R. Schomäcker, P. Saalfrank, A. Thomas, *Angew. Chem. Int. Ed.* **2021**, *60*, 19797-19803.

View Article Online
DOI: 10.1039/D5SC08299D



Data availability

The data supporting this article have been included as part of the Supplementary Information.

