Chemical Science



PERSPECTIVE

View Article Online
View Journal | View Issue



Cite this: Chem. Sci., 2020, 11, 5369

All publication charges for this article have been paid for by the Royal Society of Chemistry

Received 10th March 2020 Accepted 24th April 2020

DOI: 10.1039/d0sc01432j

rsc.li/chemical-science

Bimetallic metal—organic frameworks and their derivatives

Bimetallic metal-organic frameworks (MOFs) have two different metal ions in the inorganic nodes. According to the metal distribution, the architecture of bimetallic MOFs can be classified into two main categories namely solid solution and core-shell structures. Various strategies have been developed to prepare bimetallic MOFs with controlled compositions and structures. Bimetallic MOFs show a synergistic effect and enhanced properties compared to their monometallic counterparts and have found many applications in the fields of gas adsorption, catalysis, energy storage and conversion, and luminescence sensing. Moreover, bimetallic MOFs can serve as excellent precursors/templates for the synthesis of functional nanomaterials with controlled sizes, compositions, and structures. Bimetallic MOF derivatives show exposed active sites, good stability and conductivity, enabling them to extend their applications to the catalysis of more challenging reactions and electrochemical energy storage and conversion. This review provides an overview of the significant advances in the development of bimetallic MOFs and their derivatives with special emphases on their preparation and applications.

1. Introduction

Metal-organic frameworks (MOFs), or porous coordination polymers (PCPs), constructed from inorganic nodes with organic linkers, have emerged as a promising class of materials with high porosity, diverse composition and tuneable pore structures. ^{1,2} These characteristics have attracted significant research interest in a variety of fields, such as gas adsorption

"AIST-Kyoto University Chemical Energy Materials Open Innovation Laboratory (ChEM-OIL), National Institute of Advanced Industrial Science and Technology (AIST), Yoshida, Sakyo-ku, Kyoto 606-8501, Japan. E-mail: q.xu@aist.go.jp

backbool of Chemistry and Chemical Engineering, Yangzhou University, Yangzhou 225002, China. E-mail: qxuchem@yzu.edu.cn

and separation,³⁻⁵ catalysis,⁶⁻⁸ luminescence,⁹ sensing,¹⁶ biomedicine,¹¹ and energy.¹²⁻¹⁴

In order to enhance the catalytic, electronic, and luminescence properties of MOFs, it has been proposed to incorporate second metal ions into the nodes of frameworks for the preparation of bimetallic MOFs. ^{15,16} The partial substitution by second metal ions in the inorganic nodes or secondary-building units (SBUs) in the framework will allow the bimetallic system to show synergistic effects. In bimetallic MOFs, the proportions of the metals can be adjusted or even controlled, offering the possibility to tune the physicochemical properties of bimetallic MOFs. ^{17,18}

According to the distribution of metal ions, bimetal MOFs can adopt "solid solution" or "core-shell" structures (Fig. 1).¹⁹



Liyu Chen received his BS degree in 2013 and his PhD in 2017, both from the South China University of Technology. In August 2017, he joined Prof. Qiang Xu's group in the AIST-Kyoto University Chemical Energy Materials Open Innovation Laboratory (ChEM-OIL) as a postdoctoral researcher. His research is centered on the design and preparation of MOF-based materials and their

applications in heterogeneous catalysis.



Hao-Fan Wang received his BS and PhD degrees from the Department of Chemical Engineering, Tsinghua University in 2013 and 2018, respectively. He is currently a postdoctoral researcher in the AIST-Kyoto University Chemical Energy Materials Open Innovation Laboratory (ChEM-OIL). His research interests include carbon materials, MOF-derived materials, and their applica-

tions in electrocatalysis and metal-air batteries.

Chemical Science Perspective

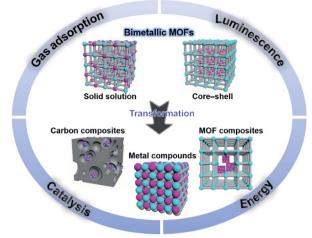


Fig. 1 Schematic organization of the main contents including bimetallic MOFs and their derivatives, and some major applications.

In solid solution bimetallic MOFs, the metals show delocalized or even homogeneous distributions through the whole crystal. Solid solution bimetallic MOFs can be synthesized by direct synthesis, post-synthetic modification and template synthesis. In core–shell bimetallic MOFs, the MOF shell is chemically different from the MOF core while they are integrated into a single architecture. Core–shell bimetallic MOFs can be synthesized through seed-induced growth of a MOF onto the surface of another, post-synthetic exchange of metal ions in the MOF surface, or one-pot synthesis. In this review, we mainly discuss the bimetallic MOFs in which both of metal ions serve as SBUs of MOFs. Bimetallic systems of immobilization of metal ions, metal nanoparticles (NPs), and metal complexes on the inorganic nodes,^{20,21} ligands,^{22–24} or inside MOF cavities^{25–27} as guests are outside of the scope of this review.^{28,29}

Bimetallic MOFs with tuneable compositions and structures have shown enhanced properties compared to their monometallic counterparts, exhibiting superior performance in many applications, including gas adsorption, catalysis, energy storage and conversion, and luminescence sensing. 15,30-32

Moreover, bimetallic MOFs can be used as precursors/ templates for the synthesis of a variety of nanostructured materials, including carbon composites, metal compounds, and MOF composites (Fig. 1).^{33,34} By selecting appropriate bimetallic MOFs and controlling the post-treatment process (e.g., pyrolysis, hydrolysis, and hydrothermal treatment), the compositions and structures of the afforded nanomaterials can be controlled. Bimetallic MOF-derived nanomaterials exhibit exposed active sites and high stability and conductivity, which can benefit their applications in the catalysis of more challenging reactions under harsh conditions and electrochemical energy storage and conversion.

This review provides an overall picture of the significant advances of bimetallic MOFs (Fig. 2). Synthetic strategies of bimetallic MOFs and their derivatives are summarized. The applications of bimetallic MOFs and their derivatives in various fields including gas adsorption, catalysis, energy storage and conversion, and luminescence sensing are also presented. This review is expected to inspire more efforts in the development of bimetallic MOFs and their derivatives for a variety of applications.

2. Synthesis of bimetallic MOFs

Many strategies have been developed for the synthesis of bimetallic MOFs. This section focuses on the synthetic strategies of both solid solution and core–shell bimetallic MOFs. For the obtained bimetallic MOFs, using appropriate physicochemical techniques is essential for characterizing the compositions, distributions, and structures of the bimetallic MOFs. X-ray diffraction (XRD) and energy-dispersive X-ray (EDX)



Caixia Li received her BS degree in 2014 and her PhD in 2019, both from Shandong University. In August 2019, she joined Prof. Qiang Xu's group in the AIST-University Chemical Kyoto Energy Materials Open Innovation Laboratory (ChEM-OIL) as a postdoctoral research fellow. Her research is focused on the design and preparation of MOFderived materials and their applications in the energy storage area.



Qiang Xu received his PhD in 1994 from Osaka University. He is the director of AIST-Kyoto University ChEM-OIL, adjunct Professor of Kobe University/Kyoto University and specially-appointed professor of Yangz-hou University. He received the Thomson Reuters Research Front Award in 2012 and Humboldt Research Award in 2019 and was recognized as a highly cited researcher (2014–2019) in

Chemistry and Engineering/Materials Science by Thomson Reuters/Clarivate Analytics. His research interests include the chemistry of nanostructured materials and their applications, especially for catalysis and energy. He is a fellow of the Engineering Academy of Japan (EAJ), European Academy of Sciences (EURASC) and National Academy of Sciences, India (NASI).

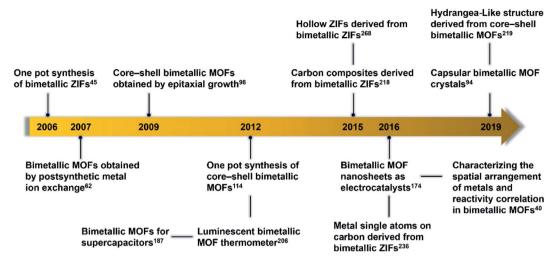


Fig. 2 Timeline of important breakthroughs regarding bimetallic MOFs and their derivatives.

mapping can be combined to identify the crystalline phases of MOFs. In accordance with Vegard's law, bimetallic MOFs show diffraction peak positions between those of monometallic MOFs. 35,36 Atomic absorption spectroscopy (AAS), inductively coupled plasma (ICP), EDX mapping and aerosol time-of-flight mass spectrometry (ATOFMS) can be coupled to calculate the global and local metal concentrations and distributions. 37,38 Xray absorption techniques, such as X-ray photoelectron spectroscopy (XPS) and X-ray absorption fine structure (XAFS), can determine the location of metals (present as nodes, bonded to the nodes, or present in the pores) in bimetallic MOFs.39 Extended X-ray absorption fine structure spectroscopy (EXAFS), neutron powder diffraction (NPD) and XPS can determine the spatial arrangements of metals in the SBUs of bimetallic MOFs. 40-42 Different techniques should be combined for the accurate characterization of the synthesized bimetallic MOFs.

2.1 Solid solution bimetallic MOFs

The term "solid solution" is used somewhat lightly, as in some cases a completely homogeneous distribution of metals may not be present.16,35,43 In this review, we divide solid solution bimetallic MOFs into two categories based on the spatial arrangements of metals: (1) two different metals are in the same SBU and the mixed metal SBUs are present throughout the MOF structure (Fig. 3A) and (2) each SBU consists of the same kind of metal and the two different SBUs are well mixed in the MOF structure (Fig. 3B). Two metals with a similar ionic radius and coordination sphere are more likely to exist in the same SBUs.44 It has been demonstrated that metals mixed in the same SBU can show stronger synergistic interactions compared to metals in different SBUs. 40 However, in many bimetallic MOFs, the specific arrangement of metals in the SBUs throughout the crystal structure remains undetermined. Nevertheless, we generally define that in solid solution bimetallic MOFs the two metals are well dispersed throughout the MOF crystal. In this section, we focus on the discussion of methodologies to prepare solid solution bimetallic MOFs.

2.1.1 Direct synthesis. Solid solution bimetallic MOFs can be directly synthesized by mixing all the metal salts during the solvothermal synthesis. ^{45–48} Using two metal salts in a one-pot reaction does not guarantee the formation of a solid solution bimetallic MOF due to the varying MOF-forming kinetics of the two metal ions. To achieve a controlled incorporation, delicate control is required to avoid the formation of mixed MOF phases. Parameters including the solubility, reactivity and coordination sphere of metal ions and the pH of the reaction mixture have significant effects on the final molar ratio of the metal ions.

A variety of bimetallic MOFs have been successfully synthesized through adding second metal precursors in the recipe of monometallic MOFs, such as $\mathrm{Co^{2^+}}$ doping into MOF-5 (IRMOF-1, $\mathrm{Zn_4O(BDC)_3}$, BDC = terephthalate) for $\mathrm{Co/MOF-5,^{49}}$ $\mathrm{Zn^{2^+}}$ doping into HKUST-1 ($\mathrm{Cu_3(BTC)_2}$, BTC = 1,3,5-benzenetricarboxylate) for $\mathrm{Zn/Cu\text{-}BTC,^{50}}$ Co doping into MOF-74 ($\mathrm{Zn_2(DOT)}$, DOT = dioxidoterephthalate) for $\mathrm{Co/MOF-74,^{51}}$ $\mathrm{Cu^{2^+}}$ doping into ZIF-67 ($\mathrm{Co(2\text{-}MeIm)_2}$, 2-MeIm = 2-methylimidazole, ZIF stands for the zeolitic imidazolate framework) for $\mathrm{Cu/ZIF-67,^{52}}$ Cu into ZIF-8 ($\mathrm{Zn(2\text{-}MeIm)_2}$) for $\mathrm{Cu/ZIF-8}$ (Fig. 4A), $\mathrm{^{53}}$ Mg $^{2^+}$ doping into MIL-101(Cr) (MIL stands for

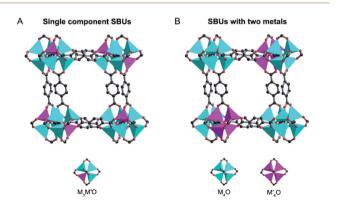


Fig. 3 Two spatial arrangements of metals in solid solution bimetallic MOFs and their SBUs.

Chemical Science Perspective

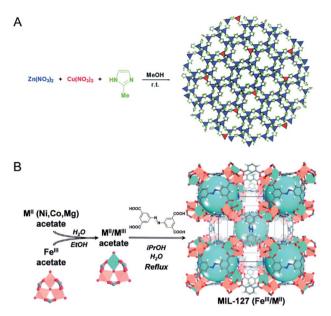


Fig. 4 (A) Schematic representation of the synthesis of Cu-doped ZIF-8 crystals. Reproduced with permission from ref. 53. Copyright 2015, Royal Society of Chemistry. (B) Schematic representation of the building block approach to produce mixed-metal carboxylate MOFs such as MIL-127. From left to right, mixing iron acetate trimeric building blocks with MII acetate compounds leads to neutral mixedmetal trimeric building blocks that are used to produce the titled MOF via acetate/ligand exchange. Reproduced with permission from ref. 60. Copyright 2015, Royal Society of Chemistry.

Materials Institute Lavoisier),54 MIL-53(Cr-Fe) [(M^{III}OH)(BDC)(H₂BDC)_x],⁵⁵ and Ce doping into UiO-66(Zr) (UiO stands for Universitetet i Oslo).56

Mixed-metal MOFs containing more than two kinds of metal ions have been achieved. Yaghi and co-workers use a one-pot reaction to make crystalline mixed-metal MOF-74 [M2(DOT)] of varying metal ions (up to 10 different metal ions) in the nodes.⁵⁷ H₄DOT and selected metal salts were dissolved in a solvent mixture of N,N-dimethylformamide (DMF), ethanol, and water, heated at 120 °C for 20-24 h, affording mixed-metal MOF-74 (MM-MOF-74) materials. It is worth mentioning that this approach allowed the incorporation of typical metal ions (i.e., Ca, Sr, Ba, and Cd) in MM-MOF-74 from which a single-metalcontaining MOF structure could not be made. XRD and SEM confirmed the pure phase of MM-MOF-74. Inductively coupled plasma-optical emission spectrometry (ICP-OES) demonstrated that MM-MOF-74 contained all metal ions added to the reaction mixture, while Ca, Sr, and Ba ions were less present because of their higher coordination number (8) than that of Mg, Mn, Fe, Co, Ni, Zn and Cd (6). EDX indicated that MM-MOF-74 crystals contained all the metals but had different distributions of the metals in each crystal.

To reach a higher degree of control over the synthesis of mixed-metal MOFs, the use of pre-defined SBUs is a promising approach to control metal stoichiometry.58-61 Feng, Bu and coworkers created a variety of In-M clusters as inorganic building blocks for fabricating five series of MOFs, CPM-18 M (M = Nd, Sm), CPM-19 M (M = Nd, Pr), CPM-20 (Co), CPM-21 M (M = Mn, Co, Cu), and CPM-23 (Mg).58 This work demonstrated the successful synthesis of bimetallic MOFs consisting of a p-block element (indium) and s-, d-, and f-block elements with differing nuclearities, metal-to-metal ratios, geometries, and charges. Serre and co-workers used oxocentered trimeric mixed iron(III)/ metal(II) acetates (M = Co, Ni, Mg) as building blocks for the scalable and green preparation of mixed-metal MIL-127 (Fig. 4B).60 They first synthesized neutral mixed metal building blocks with the general formula $Fe_{2}^{III}M^{II}O(H_{2}O)_{2}[O_{2}C-CH_{3}]_{6}$ $\cdot_n H_2O$ (with M = Co or Ni), which were then used as precursors for the synthesis of Fe/Co, Fe/Ni and Fe/Mg MIL-127 MOFs. EDX analysis indicated that the ratio of Fe(III) to metal(II) remained at ca. 2 to 1 in the obtained MOFs. A control experiment using a 2 to 1 ratio of Fe(III) and metal(II) salts under similar synthesis conditions led to either amorphous or recrystallized linkers due to the different acidity and metal-ligand bond lability between metal(III) and metal(II) cations.

2.1.2 Post-synthetic modification. Bimetallic MOFs can be fabricated by postsynthetic metal ion exchange processes, which may not be yielded through direct synthesis. 62-64 The coordination number and environment of the SBUs, the ionic radii and the valency of the metal ions, the MOF lattice and the solvent significantly affect the extent, rate, and reversibility of the exchange process. 65-68 Metal ions in an SBU with higher coordination numbers or coordinating with terminal solvent species can undergo cation exchange. 69-72 Cu2+ ions tend to replace most other second row transition metals (Zn²⁺, Cd²⁺, and Mn²⁺) due to their high electronegativity to form more covalent bonds with thermodynamic stability. 63,73,74 Cd2+ and Pb²⁺ show a faster exchange rate than Cu²⁺, owing to their low electronegativity to form labile ionic bonds.75-77 MOFs with great lattice flexibility can allow the geometrical distortions of SBUs for cation exchange. 78 Solvents with a small molecular size and relatively high ligand field strength (e.g., methanol) can accelerate the exchange rate compared with larger solvents (DMF or dimethyl sulfoxide).63,79

Long and co-workers demonstrated the concept of cation exchange of MOFs by partially exchanging Mn2+ in Mn3[(Mn4-Cl₃(BTT)₈(CH₃OH)₁₀]₂ $(1-Mn^{2+}; BTT = 1,3,5-benzenetriste$ trazolate) with selected cations.62 The MOFs were soaked in methanolic solutions of Fe²⁺, Co²⁺, Ni²⁺, Cu²⁺, Zn²⁺, Li⁺, and Cu⁺ salts at room temperature. The degree of cation exchange in 1-Mn²⁺ was determined by inductively coupled plasma-atomic absorption (ICP-AA). The 3 equiv. of Mn²⁺ in 1-Mn²⁺ could be replaced with Fe2+, Co2+, Ni2+, Cu2+, and Zn2+. However, the metathesis of Mn²⁺ with monovalent cations (Li⁺ or Cu⁺) showed incomplete exchange with Li+ or almost negligible substitution with Cu⁺ due to charge repulsion effects.

Kim and co-workers reported the complete and reversible exchange of metal ions in the SBUs of a microporous framework while maintaining the structural integrity of the framework and single crystallinity.⁷⁵ The Cd²⁺ ions in MOF 1, Cd_{1.5}(H₃O)₃[(-Cd₄O)₃(hett)₈]·6H₂O (hett = ethyl substituted truxene tricarboxylate), were exchanged with Pb2+ by immersing MOF 1 in aqueous Pb(NO₃)₂ solution. The monitoring of the ion exchange process by inductively coupled plasma atomic emission spectroscopy (ICP-AES) showed that 98% of Cd²⁺ was replaced by

Perspective **Chemical Science**

Pb²⁺ within 2 h and a complete exchange of Cd²⁺ with Pb²⁺ occurred in 2 days. A reverse exchange of Pb2+ with Cd2+ took a longer time with \sim 50% exchange of Pb²⁺ in 1 day and a complete exchange in almost 3 weeks. Moreover, the Cd²⁺ ions of MOF 1 could be exchanged with trivalent lanthanide ions (Dy3+ and Nd3+) balanced by NO3- ions without losing crystallinity.

Metal ion exchange has focused largely on MOFs that are not considered highly robust, 63,76 while it is also observed on MOFs that are considered to possess high structural stability, such as ZIFs,38 UiO-66(Zr),37,80 and MILs.81

Cohen and co-workers reported the synthesis of bimetallic ZIFs (Mn(II)-based ZIFs) through a postsynthetic exchange approach (Fig. 5A).38 ZIF-71(Zn) was incubated in a solution of Mn(acetylacetonate)₂ in MeOH to afford ZIF-71(Zn/Mn). Results showed that all of the ZIF-71 particles participated in the exchanged process with 12% of the tetrahedral Zn²⁺ centres exchanged for Mn²⁺. ZIF-8 could also exchange ~10% of Zn(II) centres for Mn(II). Cohen and co-workers also demonstrated the metal exchange of Zr4+ in UiO-66(Zr) with Ti4+ and Hf4+.37 UiO-66(Zr) was exposed to DMF solutions of different Ti⁴⁺ salts, such as $TiCp_2Cl_2$, $TiCl_4(THF)_2$, or $TiBr_4$ (Cp = η^5 -cyclopentadienyl, THF = tetrahydrofuran) for 5 days at 85 °C. The amount of exchanged Ti⁴⁺ depended on the metal salt used. TiCl₄(THF)₂ showed the highest substitution level (38 wt%), while TiBr₄ showed the lowest level due to its reactivity and instability. UiO-66(Zr) allowed very little metal ion exchange with HfCl₄ at room temperature. Even at elevated temperatures, only $\sim 20\%$ of the UiO-66(Zr) particles incorporated Hf⁴⁺.

One should keep in mind that the postsynthetic exchange of metal ions cannot always allow the replacement of metal ions in

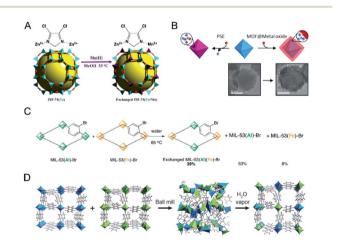


Fig. 5 (A) Postsynthetic Mn(II) exchange of ZIF-71. Reproduced with permission from ref. 38. Copyright 2013, American Chemical Society. (B) The addition of exogenous Ti⁴⁺ and Hf⁴⁺ to UiO-66 resulted in the formation of metal oxides on the surface of UiO-66 particles, giving a core-shell, MOF@metal oxide structure. Reproduced with permission from ref. 83. Copyright 2018, American Chemical Society. (C) Solid-solid postsynthetic cation exchange in MIL-53. Reproduced with permission from ref. 37. Copyright 2012, American Chemical Society. (D) A possible formation mechanism for the solid solution of Al-ndc and Ga-ndc by ball milling and vapor exposure processes. Reproduced with permission from ref. 85. Copyright 2017, Wiley-VCH.

the SBUs. The metal ions may graft onto the surface of the inorganic node at a linker vacancy site or deposit on the surface of MOFs in the form of nanoscale metal oxides (Fig. 5B).82,83 Different analytical methods should be combined to confirm the successful exchange of metal ions in the SBUs of MOFs after synthesis.

Moreover, metal exchange can also occur between two robust MOF solids. Cohen and co-workers demonstrated that robust MOFs would readily exchange their structural metal ions in a solid-solid postsynthetic exchange process (Fig. 5C).³⁷ MIL-53(Al)-Br and MIL-53(Fe)-Br as dry solids were mixed and then incubated in water for 5 days at 85 °C. ATOFMS showed that 40% of the particles contained both metal ions [i.e., MIL-53(Al/ Fe)].

In addition, mechanical milling has also been demonstrated to be a powerful tool for metal ion exchange between two solid MOFs for the synthesis of solid solution bimetallic MOFs.84-86 Horike, Kitagawa and co-workers demonstrated that solventfree mechanical milling of two MOF crystals could induce the dissolution of each metal ion into the amorphous solid state, which subsequently reconstructed to crystalline structures via vapor treatment (Fig. 5D).85 The authors prepared nine powder mixtures of Al-ndc and Ga-ndc (ndc = 1,4-naphthalenedicarboxylate) with different molar ratios from 1:9 to 9:1. The mixtures were treated by ball-milling, followed by exposure to saturated water for 3 days to form solid solution Al/ Ga-ndc materials, as determined by XRD. This method could also be applied for the preparation of other solid solution MOFs, such as Zn/Mg-MOF-74, Zn/Co-ZIF-8, and Zn/Cd-ZIF-8.

2.1.3 Template synthesis. Template methods have been employed for the synthesis of bimetallic MOFs for a good control over the arrangement of metal ions in MOFs. Coskun and co-workers employed a metal-organic polymer with welldefined binding sites for anchoring a secondary metal as a structural template and precursor for the synthesis of bimetallic MOF-74 s (Fig. 6A).87 1D metal-organic polymer 1, $[Zn(H_2O)_2(C_8H_4O_6)]_n$, was synthesized by reacting 2,5-dihydroxy-1,6-benzenedicarboxylate with ZnSO₄. The 1D polymer possessed well-defined binding sites (hydroxy and carbonyl) for the coordination of secondary metal ions (Mg²⁺ or Ni²⁺). The 1D polymer was suspended in a solution of the secondary metal precursors to get impregnated polymers, followed by transformation into 3D Zn/M-MOF-74 (M = Mg, Ni) under solvothermal conditions. The two different metal ions were homogeneously distributed in MOF-74 crystals with a constant molar ratio of 1: 1 regardless of the initial metal concentrations in the reaction mixture.

In addition to achieving a better control of the metal arrangement in bimetallic MOFs, templated synthesis can also allow the construction of hollow bimetallic MOFs. Hollow MOFs can not only inherit the merits of MOFs, but also have additional advantages such as facile mass transport and rich active sites.88 Templated synthesis methods for the synthesis of hollow MOFs can be divided into the exterior-template method and self-template method. Exterior-template synthesis of hollow MOFs usually uses a sacrificial template to prefabricate a coreshell intermediate and subsequently removes the template.89,90

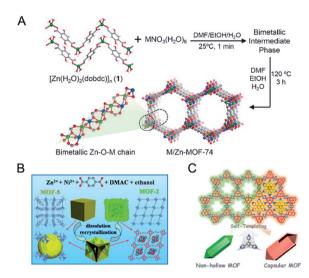


Fig. 6 (A) Synthetic strategy for the heterogeneous phase preparation of bimetallic MOF-74 structures *via* a template-directed approach, in which a 1D metal-organic polymer with well-defined binding pockets was used as a structural template for the preparation of well-ordered bimetallic MOF-74s. Reproduced with permission from ref. 87. Copyright 2017, Wiley-VCH. (B) Schematic illustration of crystal-structure transformation of a MOF combined with its shape evolution. Reproduced with permission from ref. 93. Copyright 2014, Wiley-VCH. (C) Schematic illustration for the formation of capsular-MOF from FeNi-MIL-88B. Reproduced with permission from ref. 94. Copyright 2019, American Chemical Society.

This exterior-template method has been applied for the synthesis of hollow bimetallic MOFs.91 The self-template method has also been reported for the synthesis of hollow bimetallic MOFs. 92-95 The self-template method usually goes through a dissolution-regrowth process, leading to the formation of bimetallic MOFs with hollow structures. The selftemplate method does not require a further step to remove the templates, which is simple and facile. For example, Wang and co-workers reported the synthesis of hierarchical Zn/Ni-MOF-2 nanosheet assembled hollow nanocubes (NAHNs) transformed from Zn/Ni-MOF-5 via a dissolution and recrystallization process (Fig. 6B).93 H₂BDC, Zn²⁺ and Ni²⁺ ions were dissolved in a mixed solvent of N,N-dimethylacetamide (DMAC) and ethanol. During the synthesis process, a high concentration of precursors led to a fast formation of cubic crystalline Zn/Ni-MOF-5, which was gradually etched and acted as the template for the growth of thermodynamically favoured Zn/Ni-MOF-2 nanosheets. Xu and co-workers constructed an iron-nickel-based single-crystal open capsular-MOF through a crystal-structure transformation (Fig. 6C).94 Nonhollow crystals of FeNi-MIL-88B were dispersed in a hot DMF solution of 2,4,6-tris(4-pyridyl) pyridine (tpy), affording uniform capsular-MOF nanocrystals. A detailed study of the growth mechanism revealed that the parent FeNi-MIL-88B with plenty of concave defects dissolved and released Fe3+, Ni2+, and BDC-NH22- under solvothermal conditions, followed by the construction of FeNi-MIL-88B-tpy on the surface of FeNi-MIL-88B and final formation of capsular FeNi-MIL-88B-tpy with openings in the nanocrystal walls. FeNiMIL-88B-tpy with additional size-matching ligands (tpy) in the structure showed enhanced structural stabilities compared to FeNi-MIL-88B, thus driving the dissolution–regrowth process in hot DMF.

2.2 Core-shell bimetallic MOFs

In core-shell bimetallic MOFs, the shell and core MOFs are formed from different metal centres. Three well-established strategies have been exploited for fabricating core-shell bimetallic MOFs, namely, seed-induced growth, post-synthetic exchange, and one-pot synthesis.

2.2.1 Seed-induced growth. Seed-induced growth has been demonstrated to be a powerful route for the synthesis of coreshell nanomaterials. 96,97 Two MOFs with similar lattice parameters can be assembled to form core–shell MOFs by epitaxial growth. Kitagawa and co-workers demonstrated the first synthesis of core–shell bimetallic MOF single crystals by epitaxial growth. 98 The hybrid material consisted of $[Zn_2(ndc)_2-(dabco)]_n$ (1) as the core crystal and $[Cu_2(ndc)_2-(dabco)]_n$ (2) as the shell crystal (ndc = 1,4-naphthalenedicarboxylate; dabco = diazabicyclo[2.2.2]octane) and was synthesized by immersing 1 in a solution of $CuSO_4 \cdot 5H_2O$, H_2 ndc and dabco for the growth of 2. Yamauchi and co-workers reported core–shell bimetallic ZIF materials with Zn-containing ZIF-8 as the core and Co-containing ZIF-67 as the shell (Fig. 7A). 99 Tang and co-workers

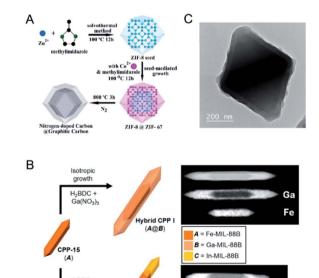


Fig. 7 (A) Synthetic scheme for the preparation of core–shell ZIF-8@ZIF-67 crystals. Reproduced with permission from ref. 99. Copyright 2015, American Chemical Society. (B) Schematic representation of the preparation of two types of heterocompositional CPPs, Hybrid CPP I (A@B) and Hybrid CPP II (C/A/C), through the isotropic and anisotropic nanoscale growth of secondary CPs on CPP-15. Here, A = Fe-MIL-88B, B = Ga-MIL-88B, and C = In-MIL-88B. Reproduced with permission from ref. 102. Copyright 2013, American Chemical Society. (C) TEM image of UiO-66@ZIF-8. Reproduced with permission from ref. 103. Copyright 2015, Wiley-VCH.

brid CPF

Perspective Chemical Science

reported a sandwich structure with an inner core and an outer shell composed of MIL-101 with metal nodes of Fe^{3+} , Cr^{3+} or both. OR Rosi and co-workers reported a domain building block (DBB) approach to construct a rich library of UiO-67 stratified MOF (sMOF) particles consisting of multiple concentric DBBs with core–shell and multilayered structures, such as UiO-67(Zr) \subset UiO-67(Hf), UiO-67(Hf) \subset UiO-67(Zr), and UiO-67(Zr) \subset UiO-67(Hf) \subset UiO-67(Zr).

Oh and co-workers further demonstrated that lattice parameter variation of isostructural MOFs could lead to different growth behaviors in an isotropic or anisotropic fashion (Fig. 7B). They employed Fe-MIL-88B as the seed to direct the formation of Ga-MIL-88B and In-MIL-88B with analogous structures but different sizes of metal ions. Ga-MIL-88B isotropically grew on the entire surface of Fe-MIL-88B, while In-MIL-88B anisotropically grew in the c-direction at both tips of Fe-MIL-88B. The different behaviors are due to the size variation of the metal ions. The ion size of Ga(III) is quite similar to that of Fe(III), resulting in a good similarity in the cell parameters for growth in an isotropic manner. However, the ion size of In(III) is larger than that of Fe(III), leading to a significant increase in the c cell parameters of In-MIL-88B and thus the anisotropic growth of In-MIL-88B in the c-direction.

The epitaxial growth method is usually limited to the synthesis of core-shell MOFs with similar crystallographic parameters. The assembly of two MOFs with different crystal structures would inevitably suffer from the separate growth of MOFs in solution. To address this issue, it has been demonstrated that the use of capping agents can promote a conformal and oriented overgrowth of one MOF on another MOF with different crystal structures. 103-105 Tsung and co-workers overgrew uniform ZIF-8 shells on monodisperse UiO-66 microcrystal cores to form UiO-66@ZIF-8 with the assistance of cetyltrimethylammonium bromide (CTAB).103 The authors proposed that CTAB could adsorb small and uniform ZIF-8 nuclei under sonication and then orient the nuclei to grow into a conformal shell (Fig. 7C). Li, Kitagawa and co-workers developed an internal extended growth method (IEGM) for the synthesis of a MOF-on-MOF structure [NH₂-UiO-66(Zr) on NH₂-MIL-125(Ti)], in which the two MOFs have distinct morphologies and crystal structures. 106 NH2-UiO-66(Zr) was exposed to NH2-MIL-125(Ti) precursors with polyvinylpyrrolidone (PVP) as the structuredirecting agent through microwave heating, resulting in the interspersion of NH2-UiO-66(Zr) particles on the NH2-MIL-125(Ti) nanotablet. During the synthesis, PVP covered NH2-UiO-66(Zr) NPs to coordinate Ti⁴⁺, thus allowing the nucleation and growth of NH2-MIL-125(Ti) around NH2-UiO-66(Zr) NPs. Various MOF-on-MOF materials, such as MIL-101(Cr) on NH₂-MIL-125(Ti), MOF-76 (Tb) on NH₂-MIL-125, could be successfully fabricated by this method.

Although capping agents can facilitate the integration of core MOFs and shell MOFs with distinct crystallographic parameters, the capping agent can potentially make the MOF–MOF interface complex and ill defined. In this regard, Zhou and co-workers reported the fabrication of MOF-on-MOF structures with mismatched lattices through retrosynthetic design without the use of capping agents.¹⁰⁷ The authors chose stable PCN-

222(Zr) (also known as MOF-545) as the core MOF, which was pretreated with linkers ($\rm H_2BDC$) of the shell MOF (MOF-5), resulting in the coordination of $\rm H_2BDC$ on the surface of PCN-222(Zr). Further adding metal precursors ($\rm Zn(NO_3)_2$) allowed the gradual formation of MOF-5 on the surface of PCN-222(Zr). This retrosynthetic method could be successfully applied to the synthesis of other MOF-on-MOF materials with stable MOFs (UiO-66 (Zr), UiO-67 (Zr), PCN-160 (Zr), MOF-808 (Zr), PCN-250 (Fe), and MIL-125(Ti)) as core MOFs and M(II) based carboxylate MOFs as the shell MOFs [MOF-177 (Zn), HKUST-1 (Cu), and MOF-1114 (Yb)] due to their mild synthetic conditions and relatively large crystal sizes.

2.2.2 Post-synthetic exchange. Post-synthetic selective exchange of metal ions in the framework can be used to synthesize core-shell bimetallic MOFs. In the MOF crystal, metal sites in the core and close to the surface show different flexibilities and thus distinct reactivities. Therefore, through carefully controlling the post-synthetic metal exchange process, core-shell bimetallic MOFs can be obtained through selective transmetalation. Lah and co-workers reported a kinetically controlled replacement of the metal in the external region of the crystal to obtain core-shell bimetallic MOFs (Fig. 8A).78 A family of isostructural MOFs, $M_6(BTB)_4(BP)_3$ (where M = Zn(II) (1), Co(II) (2), Cu(II) (3), and Ni(II) (4), BTB = 1,3,5-benzenetribenzoate, and BP = 4,4'-dipyridyl), were selected for the transmetalation reactions. Thermodynamically less stable 1 and 2 could undergo transmetalation to more stable 3 and 4, while the reverse transmetalation could not occur. The authors found that the metal sites in the external shell region of the crystal showed higher reactivities, thus reacting faster than those in the more rigid internal core. Therefore, by simply controlling the soaking time, core-shell heterostructures were formed through selective transmetalation.

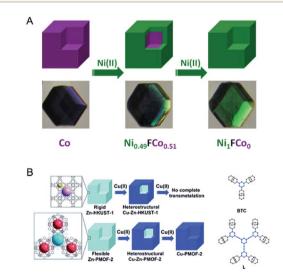


Fig. 8 (A) Synthetic scheme for the preparation of core-shell heterostructures *via* selective transmetalations. Reproduced with permission from ref. 78. Copyright 2012, American Chemical Society. (B) Transmetalations in two MOFs (Zn-HKUST-1 and Zn-PMOF-2) with different framework flexibilities. Reproduced with permission from ref. 108. Copyright 2012, Royal Society of Chemistry.

Chemical Science Perspective

In the subsequent work, Lah and co-workers further demonstrated the concept of selective transmetalation using two Zn-based MOFs with different ligand lengths, Zn-HKUST-1 and Zn-PMOF-2 (Zn₂₄L₈(H₂O)₁₂, L = 1,3,5-tris(3,5-dicarboxylphenylethynyl)benzene). In the methanol solution of Cu(II), the transmetalation of Zn-HKUST-1 was incomplete even after three months. Zn-PMOF-2 showed a higher rate and extent in the transmetalation process due to its more flexible structure compared with Zn-HKUST-1 (Fig. 8B). For both MOFs, the exchange of the metal ions occurred selectively at the external shell, leading to a core–shell heterostructure.

2.2.3 One-pot synthesis. One-pot synthesis can simplify the synthetic process and reduce steps for the separation and purification of intermediates, which is desirable but challenging. Ore—shell bimetallic MOFs can be prepared in one pot, through mixing all the precursors of core and shell MOFs in the synthesis solution. It is of vital importance to control the nucleation and growth kinetics of the two MOFs in the synthesis solution, allowing the shell MOF to grow exclusively on the surface of the core MOF without self-nucleation. The control of the experimental parameters (e.g., precursors, solvents, temperature, time, and modulators) is necessary to balance the rates of self-nucleation and growth of the core and shell MOFs, allowing them to assemble into a single nanostructure.

Zou and co-workers investigated the reaction kinetics of Co²⁺ and Zn²⁺ with 2-MeIM for bimetallic Co/Zn ZIFs (Fig. 9A).¹¹² The authors found that a low Co/Zn ratio resulted in Co-rich cores and Zn-rich shells. The growth went through a nucleation-growth separated process; Co²⁺ with higher reaction kinetics formed the cores first, followed by the growth of zinc shells. At a high Co/Zn ratio, the nucleation and growth processes were not separated, leading to a quick formation of solid solution Co/Zn ZIFs. Moreover, when adding Co²⁺ first, ZIF-67@ZIF-8/67 core-shell nanocrystals were obtained with tuneable core/shell thickness ratios. However, exchanging the sequence by adding Zn²⁺ first only formed agglomerates with irregular shapes.

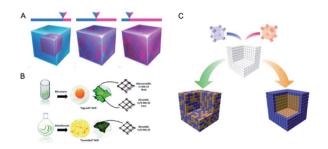


Fig. 9 (A) Schematic illustration of $Co_{20}Zn_{80}$ –ZIF, $Co_{50}Zn_{50}$ –ZIF, and $Co_{80}Zn_{20}$ –ZIF. Reproduced with permission from ref. 112. Copyright 2017, Wiley-VCH. (B) A one pot microwave procedure for creating mixed-metal "egg yolk" MOFs with a core of (Cr/V)-MIL-53 and a shell of Cr-MIL-53 (top). A solvothermal method for producing homogeneous mixed-metal MOFs (bottom). Reproduced with permission from ref. 113. Copyright 2017, Royal Society of Chemistry. (C) Schematic illustration of the construction of PCP crystals from binary crystal domain modules. Reproduced with permission from ref. 114. Copyright 2012, American Chemical Society.

Van Der Voort and co-workers reported egg-yolk bimetallic MOFs with a core of (Cr/V)-MIL-53 and a shell of Cr-MIL-53 using a one-pot microwave (MW) procedure. V³+ and Cr³+ salts were mixed with H²BDC in demineralized water in a MW for 3 h, resulting in the formation of (Cr/V)-MIL-53@ Cr-MIL-53 (Fig. 9B). For comparison, using a solvothermal method for 96 h resulted in one homogeneous phase of (Cr/V)-MIL-53 with uniform dispersion of V³+ and Cr³+. This work demonstrated that the synthesis time and method had a crucial influence on the metal dispersion in the crystals.

Kitagawa and co-workers controlled the kinetics of the crystal formation process for the preparation of core-shell MOFs in one pot by using precursors of distinct chemical reactivities (Fig. 9C). The authors employed [M(NO2-ip) (bpy)] $0.5DMF \cdot 0.5MeOH$ (MCID- $5 \supset G$, M = Zn, Mn, and Ni, NO₂-ip = 5-nitroisophthalate, and bpy = 4,4'-bipyridyl) for the study. When using 5-nitroisophthalic acid (H2NO2-ip) as a precursor, the crystal formation rate of ZnCID-5⊃G was much quicker than that of MnCID-5⊃G. The one-pot reaction of H₂NO₂-ip and bpy with zinc and manganese perchlorate salts was conducted in a DMF/MeOH solution at 70 °C for 3 days, yielding crystals with a Zn-rich inner core and a Mn-rich outer shell. During the synthesis of $Zn/MnCID-5 \supset G$, the nucleation process was dominated by the Zn rich crystals, which could facilitate the heterogeneous nucleation and growth of Mn-rich crystals. Moreover, additionally adding the precursors of NiCID-5⊃G with a moderate formation rate could yield Zn/Ni/MnCID-5⊃G crystals with a sandwich structure.

3. Applications of bimetallic MOFs

The mixing of metals in the SBUs of a MOF structure is widely recognized as an effective way to achieving optimal catalytic, optical, and electronic properties. A number of composition–property relationships have been established for many different MOF families.

The incorporation of second metal ions in the unstable SBUs of MOFs may enhance the stability of MOFs. For example, MOFs constructed from zinc(II) paddlewheel [Zn₂(OCO)₄] SBUs frequently with low stability can show enhanced stability when exchanging the Zn^{II} ion for other metal ions (such as Cu²⁺ and Ni²⁺). $^{64,115-117}$ Mg-MOF-74 can gain improved water stability by the incorporation of Ni²⁺ or Co²⁺ ions that are less likely to hydrolyze than Mg²⁺. 118

The flexibility of MOFs can be modulated by adopting different metal ions in the SBUs to meet the requirements of desired applications, such as storage, separation, and sensing. 119 Yeung, Goodwin and co-workers studied the thermal expansion in Zn/Cd ZIF-8. 35 The coefficient of thermal expansion showed a continuous and monotonic decrease with the increase of Cd content in Zn/Cd ZIF-8. These results demonstrated that Cd substitution in ZIF-8 made the framework structure increasingly flexible, due to a weaker bonding of Cd²⁺ with 2-MeIM compared with Zn²⁺. Serre and co-workers reported the tuning of the breathing behaviour of MIL-53 by cation mixing. 55 MIL-53(Cr–Fe) adopted a hydrated narrow pore (np) form below 343 K, and then changed to a closed pore (cp)

form at 343 K and a large pore (lp) form upon further heating above 463 K. This breathing behaviour is different from that of MIL-53(Cr) and MIL-53(Fe), which showed a direct np to lp transformation and a two-step np to cp transformation, respectively.

The electronic properties of MOFs can be tailored through metal node engineering.120,121 Mixing different metals in the SBUs of MOFs may provide MOFs with excellent electrical conductivity for a variety of applications, such as semiconductors, supercapacitors, thermoelectrics, and resistive sensing. Chen, Shustova and co-workers prepared bimetallic MOFs, $Cu_{3-\nu}M_{\nu}(BTC)_2$ (M = Co, Zn), and studied how the substitution of a secondary metal would affect the electronic properties of MOFs. 122 Monometallic M-MOFs (M = Cu and Zn) and bimetallic CuZn-MOFs exhibited zero intensity near the Fermi level which were characteristic of insulators, while CuCo-MOFs exhibited semiconductor behaviour. Microwave conductivity measurements showed that effective conductivities were 0.1×10^{-4} and 3.5×10^{-4} S cm⁻¹ for Cu₃(BTC)₂ and Cu_{2.4}-Co_{0.6}(BTC)₂, respectively. Density functional theory (DFT) calculations revealed that the Co incorporation into the Cu-BTC matrix resulted in a decrease in the band gap and thus a higher conductivity.

Bimetallic MOFs show enhanced physical and chemical properties due to the synergistic effect of the two metals. The remarkable features of bimetallic MOFs make them suitable for applications in a variety of fields, including gas adsorption, catalysis, energy storage and conversion, and luminescence sensing.

3.1 Gas adsorption

Perspective

Developing efficient porous materials for gas adsorption is fundamentally and industrially important. Bimetallic MOFs with large surface areas, adjustable pore sizes, and open metal sites are promising candidates as adsorbents for gas adsorption. Moreover, the adsorption strength of a specific adsorbate in bimetallic MOFs can be optimized through tuning the compositions of bimetallic MOFs. Many bimetallic MOFs have been designed as excellent adsorbents for gas adsorption.

3.1.1 Hydrogen adsorption. The hydrogen (H_2) uptake of bimetallic MOFs is highly related to the structure of MOFs to store H_2 and the unsaturated metal sites to bind with H_2 .⁵⁹

Singh and co-workers prepared $\text{Co}_x\text{Zn}_{100-x}\text{-ZIF-8}$ with varying Co contents (x=0,25,50,75,90 and 100). CoZn-ZIF-8 showed an enhancement of the surface area by $\sim 40\%$ and the pore volume by $\sim 33\%$ as compared to monometallic Zn-ZIF-8. At 77 K and 1 bar, $\text{Co}_{75}\text{Zn}_{25}\text{-ZIF-8}$ showed an enhancement of $\sim 23\%$ in the H_2 uptakes as compared to Zn-ZIF-8 (Fig. 10A). The enhanced H_2 uptake capacities of CoZn-ZIF-8 could be attributed to the enhanced pore volume, surface area, microporosity, and heterogeneity in the pores.

Botas and co-workers prepared MOF-74 with different Co contents in the range of 0–100% for $\rm H_2$ adsorption at 0 °C and 10 bar.⁵¹ The $\rm H_2$ adsorption capacity of ZnCo-MOF-74 generally increased with the increase of Co content. The authors found a correlation between the isosteric heat of adsorption ($Q_{\rm st}^{0}$) for

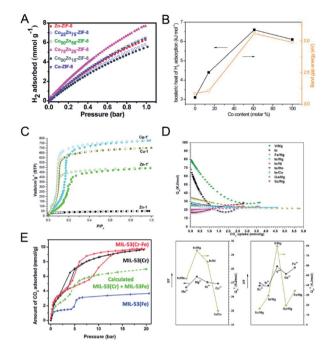


Fig. 10 (A) H_2 uptake isotherms of Zn–ZIF–8, Co–ZIF–8 and CoZn–ZIF-8 at 77 K. Reproduced with permission from ref. 123. Copyright 2016, Royal Society of Chemistry. (B) Hydrogen isosteric heat of adsorption, $Q_{\rm st}$ and band gap energy at 1.5% H_2 coverage *versus* Co content (x) in Zn_{1-x}Co_xMOF-74. Reproduced with permission from ref. 51. Copyright 2011, Elsevier. (C) CO₂ (195 K) adsorption isotherms of activated **Zn-1**, **Zn-1'**, **Cu-1**, and **Cu-1'**. Reproduced with permission from ref. 125. Copyright 2017, American Chemical Society. (D) Isosteric heat for CO₂ for CPM-200s (top). Correlation between the isosteric heat at zero loading of CO₂ ($Q_{\rm st}^{0}$) and the charge-to-radius ratio (*z/r*) of metal ions for CPM-200 s (bottom). Reproduced with permission from ref. 126. Copyright 2016, American Chemical Society. (E) CO₂ sorption isotherms at 283 K for the MIL-53 materials. Reproduced with permission from ref. 55. Copyright 2012, Royal Society of Chemistry.

 $\rm H_2$ and the band gap energy values of $\rm Zn_{1-x}Co_xMOF-74$ (Fig. 10B), implying that $\rm H_2$ -metal cluster interactions have a more decisive role in $\rm H_2$ adsorption.

Long and co-workers exchanged Mn^{2+} ions in $Mn_3[(Mn_4-Cl)_3(BTT)_8(CH_3OH)_{10}]_2$ with selected cations $(M=Li^+,Cu^+,Fe^{2+},Co^{2+},Ni^{2+},Cu^{2+},Zn^{2+})$ to tune the interaction strength between H_2 and unsaturated metal centres in the frameworks. Fe All the materials showed similar H_2 uptakes ranging from 2.00 wt% to 2.29 wt% at 77 K and 900 torr. However, the materials showed significantly different uptake slopes at very low pressure, indicating different metal–hydrogen binding strengths in the materials. The results showed that Mn^{2+} , Fe^{2+} , and Co^{2+} ions yielded the strongest H_2 binding among the cations studied.

3.1.2 Carbon dioxide adsorption. Developing adsorbents with high physicochemical stabilities, high carbon dioxide (CO_2) capacity and selectivity, and low regeneration costs is still a challenge. MOFs are promising porous crystalline materials with high porosities, surface areas and open metal sites for CO_2 capture. 124

The incorporation of a second metal in MOFs can improve the stability of MOFs and provide stronger interaction with CO₂. Chemical Science Perspective

Sun and co-workers used the metal ion exchange strategy to fabricate bimetallic MOFs with improved stability and CO2 adsorption capacity. 125 ZnII ions in Zn-1 ([Zn₃(L)₂(dabco)(H₂O)]· 9DMF, $H_3L = [1,1':3',1''-terphenyl]-4,4'',5'-tricarboxylic acid)$ were partially replaced by Cu^{II} ions to fabricate bimetallic **Zn-1**'. The copper(II) analogue, Cu-1, was exchanged with ZnII ions to fabricate Cu-1'. Zn-1' showed an enhanced N2 adsorption amount (2063 m 2 g $^{-1}$) than **Zn-1** (59 m 2 g $^{-1}$), due to the high stability of the hybrid framework. Cu-1 and Cu-1' showed similar N2 adsorption amounts. At 195 K and 1 bar, the CO2 uptakes of Zn-1, Zn-1', Cu-1, and Cu-1' were 52, 490, 703, and 770 m³ g⁻¹, respectively. Both bimetallic **Zn-1**' and **Cu-1**' exhibited improved adsorption capacities than their pristine counterparts. Moreover, bimetallic Zn-1' and Cu-1' showed large hysteresis in the CO₂ adsorption (Fig. 10C), implying enhanced interactions between the frameworks and CO2 molecules. Xiao, Li and co-workers doped Mg in MIL-101(Cr) to synthesize bimetallic MIL-101(Cr, Mg), showing improved CO₂ adsorption capacity.54 The CO2 adsorption capacity of MIL-101(Cr, Mg) reached 3.28 mmol g⁻¹ at 298 K and 1 bar, with an increase of 40% in comparison with MIL-101(Cr). The enhanced CO₂ adsorption of MIL-101(Cr, Mg) was attributed to the higher surface area and stronger adsorptive sites for CO2 due to the doping of Mg.

Bu, Feng and co-workers reported the cooperative effect of dissimilar metals in the SBUs of MOFs for CO₂ adsorption. ¹²⁶ The authors prepared a family of isostructural heterometallic MOFs ($\rm M^{II}_2M^{III}(\mu_3\text{-}OH)(CO_2)_6$, CPM-200 series, CPM = crystalline porous materials) with combinations of trivalent ($\rm In^{3+}$, $\rm Ga^{3+}$, $\rm Fe^{3+}$, $\rm V^{3+}$, and $\rm Sc^{3+}$) and divalent metals ($\rm Mg^{2+}$, $\rm Mn^{2+}$, $\rm Co^{2+}$, and $\rm Ni^{2+}$) in the SBUs. ¹²⁶ At 273 K and 1 bar, the CO₂ uptakes of the CPM-200 series, in cm³ g⁻¹, were in the order of -Fe/Mg (207.6) > -In/Mg (190.8) > -V/Mg (155.4) > -In/Co (136.9) > -Ga/Mg (136.2) > -In/Mn (126.5) > -Sc/Mg (122.4) > -In/Ni (100.4). Among the CPM-200 series, CPM-200-Sc/Mg showed the highest $Q_{\rm st}^0$ for CO₂ (-79.6 kJ mol⁻¹). The authors demonstrated a strong correlation between the charge-to-radius ratio (z/r) of metal ions in MOFs and $Q_{\rm st}^0$ for CO₂ (Fig. 10D).

In addition to the open metal sites, the pore architecture is of vital importance for CO_2 capture performance. Hill and coworkers reported the exchange of Zr in UiO-66 for Ti to yield bimetallic UiO-66 with a smaller pore size and higher adsorption enthalpy for an enhanced CO_2 uptake. With the increase of Ti substitution, the octahedral cages shrank by ~ 1 Å and became increasingly broader. The CO_2 uptake at 273 K of UiO-66(Zr₁₀₀), UiO-66(Ti₃₂) and UiO-66(Ti₅₆) was 2.2, 2.3 and 4 mmol g⁻¹, respectively. Considering that theoretical enhancement in the CO_2 gravimetric uptake of UiO-66(Ti₁₀₀) is $\sim 19\%$ while UiO-66(Ti₅₆) showed an enhancement of 81% compared with UiO-66(Zr₁₀₀), the authors proposed that both the decrease of pore sizes and stronger adsorption characteristics of Ti(Iv) contributed to the enhanced CO_2 uptake in Ti-exchanged UiO-66.

Moreover, the structural flexibility change of bimetallic MOFs will lead to a different CO₂ sorption behaviour compared with their single cation analogues. Serre and co-workers reported different CO₂ sorption isotherms of bimetallic MIL-53(Cr–Fe) compared to monometallic MOFs (Fig. 10E).⁵⁵ CO₂

sorption tests at 283 K showed that the np to lp transition of MIL-53(Cr-Fe) occurred at a pressure of \sim 10 bar, which was an intermediate between those of MIL-53(Cr) (3 bar) and MIL-53(Fe) (20 bar). This result demonstrated that MIL-53(Cr-Fe) was an intermediate between MIL-53(Cr) ('easy' to open) and MIL-53(Fe) ('hard' to open) in terms of ease of pore opening.

3.2 Catalysis

3.2.1 Organocatalysis. The use of the inorganic nodes of MOFs as catalytically active sites has several advantages, including a good dispersion of the inorganic nodes within the framework to well expose the active sites and a well-defined structure of the inorganic nodes for precise structural characterization and computational modeling. 127,128 When using monometallic MOFs as catalysts, the metal ions in the inorganic nodes need to undergo a change of the coordination environment, which may sometimes lead to the collapse of the frameworks. It is a good idea to design a bimetallic MOF, in which one metal contributes to structural stability and the other metal acts as an active centre for catalysis. This design can also allow the isolation and stabilization of active metal sites to achieve high activity, selectivity and stability. 129-135 For example, Chen and coworkers prepared $(Cu_xRu_{1-x})_3$ -(BTC)₂ (CuRhBTC) for propylene hydrogenation.136 CuRh(33%)BTC exhibited an activity of 1600 μ mol $g_{catalyst}^{-1}$ min⁻¹ for propane production. The CuBTC MOF showed no activity under the reaction conditions, and RhBTC was unstable upon exposure to air. The inactive Cu ions in CuRhBTC played an important role in stabilizing the MOF framework and preventing the reduction of the incorporated Rh²⁺.

Although catalytically active metal ions can be introduced through immobilization on the SBUs or organic linkers, the incorporation of a second metal on the SBUs of MOFs for bimetallic MOFs results in distinct catalytic properties compared with other ways. In this regard, Farha, Hupp, Nguyen and co-workers compared the catalytic activity of UiO-66(Zr) functionalized with Ti^{IV} ions as part of the node (Ti-UiO-66), attached to the node (UiO-66- Ti_{ex}), and on the organic linker (UiO-66-Cat-Ti) in the oxidation of cyclohexene. These three materials had Ti^{IV} ions with different coordination environments at different sites of the UiO-66 support (Fig. 11A). Three UiO-66-based catalysts showed the catalytic activity in the order of Ti-UiO-66 \gg UiO-66-Cat-Ti > UiO-66-Ti $_{ex}$, indicating that tetrahedral Ti^{IV} ions were more active than the more saturated octahedral Ti^{IV} ions.

Monometallic MOF catalysts usually exhibit either unsatisfactory activity or selectivity. Bimetallic MOFs can show a synergistic effect between the two metal ions to activate the reactants and reduce the reaction energy barrier in heterogeneous catalysis.³¹ Bimetallic MOFs have shown promising catalytic performances in a variety of reactions, including oxidation reactions, ^{56,76,138–141} reduction reactions, ^{142,143} condensation reactions, ^{144–146} addition reactions, ^{53,147} and substitution reactions

Zhu, Fan and co-workers applied bimetallic MOF-74(Cu/Co) with different Cu/Co ratios in styrene oxidation with O₂

Perspective **Chemical Science**

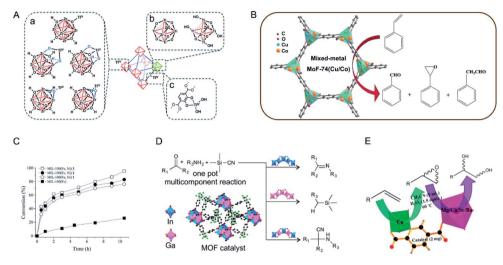


Fig. 11 (A) Proposed structures for Ti^V ions supported on the nodes (a), as the nodes (b), and on the struts (c) of UiO-66. Reproduced with permission from ref. 137. Copyright 2015, Royal Society of Chemistry. (B) MOF-74(Cu/Co) with different Cu/Co ratios as catalysts in the oxidation of styrene with O2 under solvent-free and mild reaction conditions. Reproduced with permission from ref. 139. Copyright 2016, Elsevier. (C) Time conversion plot of β -pinene, using as a catalyst either the mixed-metal MIL-100(Fe, Ni) 1–3 or homometallic MIL-100(Fe). Reproduced with permission from ref. 144. Copyright 2019, Royal Society of Chemistry. (D) Different behaviours of GaPF-1, InPF-11 β and In_xGa_{1-x}MOF as heterogeneous catalysts in the three-component, one pot Strecker reaction. Reproduced with permission from ref. 149. Copyright 2015, American Chemical Society. (E) Bimetallic MOFs with two different metals catalyzing two kinds of reactions, viz., olefin to its epoxide followed by epoxide ring opening to afford the corresponding vicinal diol in a sequential manner. Reproduced with permission from ref. 150. Copyright 2016, American Chemical Society.

(Fig. 11B).139 MOF-74(Cu) showed a low catalytic activity (0.6% conversion) but an absolute selectivity for benzaldehyde. MOF-74(Co) possessed a high catalytic activity (47.3% conversion) but a low selectivity (35%) for benzaldehyde. The incorporation of Co²⁺ in MOF-74 (Cu) could significantly enhance the conversion of styrene. With the increase of Co²⁺ content in MOF-74(Cu/Co), the conversion of styrene increased while the selectivity for benzaldehyde decreased. A physical mixture of MOF-74(Cu) and MOF-74(Co) exhibited a lower activity than MOF-74(Cu/Co), indicating the synergistic effect of Cu²⁺ and Co²⁺ in the same framework.

Garcia, Serre and co-workers synthesized a series of MIL-100(Fe, Ni) materials with different metal ratios as catalysts for the Prins reaction.144 MIL-100(Fe, Ni) (1-3) samples contained a Ni amount of 1%, 3%, and 5%, respectively. In the Prins reaction between β-pinene and paraformaldehyde, monometallic MIL-100(Fe) only showed a low conversion (<20%). Bimetallic MIL-100(Fe, Ni) afforded higher conversions between 70 and 100%. MIL-100(Fe, Ni) 3 with the highest Ni percentage showed the highest activity, with a total conversion to nopol in 10 h (Fig. 11C). The authors proposed that the incorporation of Ni^{II} could cause the distortion of the framework to facilitate the access to the Fe^{III} sites, thus enhancing the catalytic activity of the catalyst.

Park and co-workers synthesized a solid solution Zn-Co ZIF (CZ-ZIF) for chemical fixation of CO2.147 In the cycloaddition reaction of CO2 with epichlorohydrin (ECH), ZIF-8 showed an excellent ECH conversion of 98% but a low selectivity of 33% towards epichlorohydrin carbonate (ECC). ZIF-67 exhibited high selectivity to ECC (98%) but an inferior conversion of 66%. Solid solution CZ-ZIF afforded both high conversion of ECH

(94%) and high selectivity (98%) to the desired ECC. The bimetallic CZ-ZIF could combine the advantageous properties of Zn (high activity) and Co (high selectivity and low leaching), achieving enhanced catalytic performance compared to its monometallic counterparts.

Multicomponent reactions and cascade reactions which require the cooperation of different active sites can be accomplished in bimetallic MOFs. 149-152 Monge and co-workers demonstrated the control of the catalytic activity and selectivity of bimetallic MOFs in a multicomponent one pot Strecker reaction by modulating specifically selected metal ratios (Fig. 11D).149 In the A3 reaction between benzaldehyde, trimethylsilyl cyanide (TMSCN), and aniline, monometallic GaPF-1 [Ga(OH)(hfipbb)] and InPF-11 β [In(O₂C₂H₄)_{0.5}(hfipbb)] (H₂hfipbb = 4,4'-(hexafluoroisopropylidene) bis(benzoic acid)) gave only aldehyde cyanosilylation and imine as the main product, respectively. Solid-solution bimetallic MOFs [In_xGa_{1-x}(O₂C₄- $H_4)_{0.5}$ (hfipbb), x = 0.72, 0.55, and 0.28 could selectively yield the final Strecker product (α-aminonitrile) with different reaction rates. InGaPF-3 with the least amount of In showed the highest reaction rate, with 96% conversion in 0.33 h. Koner and co-workers reported a series of bimetallic MOFs based on copper and alkaline-earth metals (Mg, Ca, Sr, and Ba) to effectively catalyse olefin epoxidation and subsequent epoxide ring opening (Fig. 11E).150 In the tandem reaction, CuII acted as an active centre in epoxidation reactions and alkaline-earth metal ions served as Lewis acidic sites for epoxide ring opening subsequently. These MOFs with different alkaline-earth metals showed different reaction rates, increasing in the order of Mg < Ca < Sr \approx Ba. The authors proposed that the increase of the size of the alkaline-earth metals led to a greater number of ligands

Chemical Science Perspective

accommodated in the coordination sphere and thus formed more open sites to enhance the catalytic activity.

3.2.2 Photocatalysis. Bimetallic MOFs can also act as excellent catalysts for photocatalytic reactions, such as organic reactions, water splitting, ${\rm CO_2}$ reduction, and organic pollutant degradation.

Ti-based MOFs have shown great promise in photocatalysis. The incorporation of second metal ions in the SBUs of Ti-based MOFs can greatly enhance the photocatalytic activity. Martí-Gastaldo and co-workers reported two Ti-based MOFs (MUV-10, ${\rm Ti^{IV}}_3{\rm M^{II}}_3(\mu_3\text{-O})_2({\rm btc})_4\text{-}({\rm H}_2{\rm O})_6$, ${\rm M}={\rm Ca^{II}}$, ${\rm Mg^{II}}$) by metal doping for photocatalytic H $_2$ production (Fig. 12A). The authors found that heterometallic clusters served as excellent platforms to manipulate the electronic structure and in turn regulate the photoactivity. MUV-10(Mn) could produce 6500 μ mol g $^{-1}$ of H $_2$ after 24 hours under the irradiation of a Xe lamp (300 W), showing two times higher activity than that of MUV-10(Ca). However, few Ti-based MOFs have been reported due to the high reactivity of Ti precursors. Alternatively, Ti can be incorporated into MOFs through post-synthetic exchange

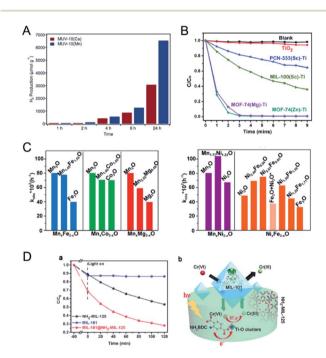


Fig. 12 (A) Photocatalytic generation of hydrogen after 24 hours of irradiation using MUV-10(Ca) and MUV-10(Mg). Reproduced with permission from ref. 153. Copyright 2018, Wiley-VCH. (B) Photodegradation of MB using no catalyst (blank), TiO2, PCN-333(Sc)-Ti, MIL-100(Sc)-Ti, MOF-74(Zn)-Ti and MOF-74(Mg)-Ti with 300 W xenon light irradiation. Reproduced with permission from ref. 158. Copyright 2016, Royal Society of Chemistry. (C) Comparison between k_{obs} of MTV-MOFs in a domain metal arrangement (left) and wellmixed metal arrangement (right) and those of their corresponding single component MOFs. Reproduced with permission from ref. 40. Copyright 2016, American Chemical Society. (D) Adsorption and photocatalytic degradation toward CrVI with MIL-101, NH2-MIL-125, and MIL-101@NH2-MIL-125 (a). Illustration of the enhanced photocatalytic degradation process towards CrVI with micro/mesoporous MIL-101@NH₂-MIL-125 materials (b). Reproduced with permission from ref. 106. Copyright 2017, Wiley-VCH.

methods. For example, Ti-substituted UiO-66 (Zr/Ti) materials have shown enhanced photocatalytic performance compared to monometallic UiO-66(Zr).¹⁵⁴⁻¹⁵⁷ Zhou and co-workers synthesized four Ti based-MOFs, PCN-333(Sc)-Ti, MIL-100(Sc)-Ti, MOF-74(Zn)-Ti and MOF-74(Mg)-Ti, using a high valence metathesis and oxidation (HVMO) method for photodegradation of methylene blue (MB).¹⁵⁸ The metal exchange ratios of PCN-333(Sc), MIL-100(Sc), MOF-74(Zn) and MOF-74(Mg) were 85.9%, 52.0%, 100%, and 35.1%, respectively (Fig. 12B). PCN-333(Sc)-Ti and MIL-100(Sc)-Ti showed 35% and 64% degradation of MB under a 300 W Xe lamp for nine minutes, respectively. MOF-74(Zn)-Ti and MOF-74(Mg)-Ti both showed conversions up to 98% in three minutes. All the synthesized Ti based-MOFs showed enhanced activities compared to TiO₂ and monometallic MOFs.

Deng and co-workers demonstrated the synergistic effect of two different metals within the SBUs of MOFs for the photooxidation of 1,5-dihydroxynaphthalene (DHN).40 The authors synthesized a series of multivariate MOFs (MTV-MOFs) with a formula of (M₃O)₂(TCPP-M)₃ (TCPP = tetrakis (4-carboxyphenyl) porphyrin). MTV-MOFs composed of Mn_xNi_{3-x}O and Ni_rFe_{3-r}O SBUs showed a well-mixed spatial arrangement of metals, which exhibited enhanced conversion rates compared to their corresponding single component MOFs. Detailed characterization demonstrated that band gaps changed dramatically when different metals were present in the same SBU with a synergistic effect, leading to effective electron/hole transfer to oxygen for a high reaction rate. For comparison, in the case of MTV-MOFs composed of $Mn_xFe_{3-x}O$, $Mn_xCo_{3-x}O$ and $Mn_xMg_{3-x}O$ SBUs, the two kinds of metals were in different SBUs and thus showed negligible interactions due to the separation by organic linkers (Fig. 12C). Therefore, these bimetallic MOFs exhibited the highest catalytic rates among their corresponding single component MOFs.

Core-shell MOFs have been successfully applied in photocatalysis, in which the shell MOF can accumulate/recognize reactants and the core MOF with catalytically active sites can transform the reactants to products.106,107,159 Kitagawa and coworkers applied MIL-101(Cr)@NH2-MIL-125(Ti) in the adsorption-photocatalytic removal of CrVI (Fig. 12D).106 MIL-101(Cr) @NH2-MIL-125(Ti) showed enhanced adsorption capacity on Cr^{VI} (3.16 mg g⁻¹) compared to those of NH₂-MIL-125(Ti) (1.12 ${\rm mg~g^{-1}})$ and MIL-101(Cr) (1.28 ${\rm mg~g^{-1}}).$ MIL-101(Cr)@NH $_2$ -MIL-125(Ti) removed 72% of CrVI from the solution under visible light irradiation. However, MIL-101(Cr) showed no activity and NH₂-MIL-125(Ti) removed only 47% of Cr^{VI} under similar conditions. The MOF on MOF heteroarchitecture could combine the high adsorption capacity of MIL-101(Cr) and photocatalytic activity of NH2-MIL-125(Ti) to exhibit high efficiency in photocatalysis.

3.2.3 Electrocatalysis. Bimetallic MOFs have been designed for electrocatalysis, such as the oxygen reduction reaction (ORR), 160 oxygen evolution reaction (OER), $^{134,161-166}$ hydrogen evolution reaction (HER), 167,168 and electrochemical CO₂ reduction. 169,170

In bimetallic MOFs, the electron configurations and d-band centres can be tailored through the mix of different metals in Perspective

the SBUs, offering opportunities to enhance the electrocatalytic performance. 122,171 Li, Lan and co-workers prepared four isostructural MOFs (NNU-21-24) based on Fe_2M (M = Fe, Co, Ni, Zn) clusters bridged with biphenyl-3,4',5-tricarboxylic acid (BPTC) ligands for the electrocatalysis of the OER. 163 Among the four synthesized MOFs, monometallic NNU-21 (Fe₃-BPTC) showed lower OER performance than bimetallic MOFs (NNU-22 (Fe₂Co-BPTC), NNU-23 (Fe₂Ni-BPTC) and NNU-24 (Fe₂Zn-BPTC)) (Fig. 13A). NNU-23 exhibited the best OER performance with an overpotential of 365 mV at a current density of 10 mA cm⁻² in 0.1 M KOH. Moreover, all the catalysts exhibited high stability with almost no decrease of activity after 2000 cycles. DFT calculation revealed that the incorporation of a second metal (Co, Ni or Zn) into the Fe cluster could induce the d-band

centre to be close to the Fermi level, leading to a stronger

binding interaction between the O* intermediate and catalysts,

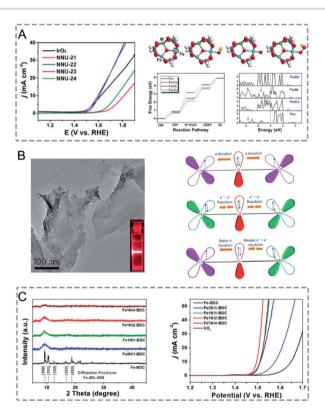


Fig. 13 (A) LSV curves of IrO₂ and NNU-21-24 for the OER in 0.1 m KOH (left). Initial structure of the Fe₂M cluster, followed by the adsorption of OH*, O*, and OOH* intermediates on the Fe site. The active site is marked by a dashed circle. The free energy profile for the OER pathway and projected density of states of the Fe₂M-cluster (right). Red arrows denote the d-band center. Reproduced with permission from ref. 163. Copyright 2018, Wiley-VCH. (B) TEM image of NiCo-UMOFNs (left). Schematic representation of the electronic coupling between Co and Ni in UMOFNs (right). Reproduced with permission from ref. 174. Copyright 2016, Nature Publishing Group. (C) XRD patterns of Fe-BDC, Fe₂Ni₁-BDC, Fe₁Ni₁-BDC, Fe₁Ni₂-BDC, and Fe₁Ni₄-BDC (diffraction positions of Fe-MIL-88B are shown in the bottom) (left). LSV curves of Fe-BDC, Fe₂Ni₁-BDC, Fe₁Ni₂-BDC, Fe₁Ni₂-BDC, Fe₁Ni₂-BDC, Fe₂Ni₃-BDC, Fe₂Ni₃-BDC, Fe₃Ni₄-BDC, Fe₃Ni₄-BDC, Fe₃Ni₄-BDC, Fe₄Ni₅-BDC, Fe₄Ni₅-BDC, Fe₅Ni₅-BDC, Fe₆Ni₆-BDC, Fe₆Ni BDC, Fe_1Ni_4 -BDC, and IrO_2 in 1 M KOH at a scan rate of 5 mV s^{-1} (right). Reproduced with permission from ref. 164. Copyright 2019, American Chemical Society.

thus improving the OER performance. In addition to solid solution bimetallic MOFs, MOF@MOF structures can also show a synergistic effect in electrocatalysis. 172 Zhu, Sun and coworkers grew Fe-MOF NPs onto Ni-MOF nanosheets (Ni-MOF@Fe-MOF) for the OER. 173 The deposition of catalytically inert Fe-MOF on Ni-MOF could enhance the electrocatalytic performance. Ni-MOF@Fe-MOF exhibited an overpotential of 265 mV to reach a current density of 10 mA cm⁻² in 1.0 M KOH, which was lower than that of Ni-MOF (370 mV). The enhanced performance of Ni-MOF@Fe-MOF could be attributed to the synergistic effect between Ni active centres and Fe species.

However, bimetallic MOFs usually suffer from poor conductivity, blockage of active metal centres by organic linkers, and low stability, which dramatically limit their utilization as electrocatalysts. To address these challenges, thinning bimetallic MOFs into nanosheets, fabricating an amorphous structure with plenty of defects, and integrating bimetallic MOFs with conductive supports have been proposed to enhance the electrocatalytic performance of bimetallic MOFs.

Thinning bimetallic MOFs into two-dimensional (2D) nanosheets can enhance mass transport and electron transfer and maximize unsaturated metal sites on the surfaces to improve the electrocatalytic performance.8,160,174-177 Liu, Zhao, Tang and co-workers reported ultrathin NiCo bimetallic MOF nanosheets (NiCo-UMOFNs) as effective electrocatalysts for the OER (Fig. 13B).¹⁷⁴ NiCo-UMOFNs on a glassy-carbon electrode showed an overpotential of 250 mV at a current density of 10 mA cm⁻² in 1.0 M KOH solution, smaller than those of Ni-UMOFNs (321 mV), Co-UMOFNs (371 mV), bulk NiCo-MOFs (317 mV) and commercial RuO₂ (279 mV). XAFS analysis and DFT calculations demonstrated that the coordinatively unsaturated metal atoms were the dominating active centres and the synergistic effect between Co and Ni further improved the electrocatalytic OER activity. Electron transfer from the Ni²⁺ sites to the Co²⁺ sites could enhance the interaction between Ni2+ sites and water, thus offering a lower energy barrier for water oxidation. Oh and co-workers prepared bimetallic conductive 2D MOFs (CoxNiv-CATs) with varied ratios of Co²⁺ to Ni²⁺ for the ORR in 0.1 M NaClO₄ and 0.02 M PBS electrolytes. 160 Ni-CAT showed a high onset potential of 0.47 V (vs. the reversible hydrogen electrode, RHE, the same below if not mentioned), but a low diffusion limiting current density at $0.0 \text{ V} (-3.62 \text{ mA cm}^{-2})$. However, Co-CAT displayed a high diffusion limiting current density (-5.59)mA cm $^{-2}$) but a low onset potential (0.42 V). Bimetallic Co_{0,27}Ni_{0,73}-CAT combined the advantages of Co-CAT (effective adsorption for O2) and Ni-CAT (high conductivity), showing a diffusion-limiting current density (-5.68 mA cm⁻²) and an onset potential (0.46 V). With the increase of the proportion of Ni from 50% to 73%, the onset potential of Co_xNi_y -CATs showed a slight increase. Further increasing the proportion of Ni to 86% resulted in a decrease in diffusion-limiting current density. Rotating ring disk electrode (RRDE) investigation showed that the electron transfer number of Co-CAT, Ni-CAT, and $Co_{0.27}Ni_{0.73}$ -CAT was 3.91, 3.31, and 3.95, respectively. The bimetallic Co_{0,27}Ni_{0,73}-CAT was more preferable for a fourelectron process.

In MOFs with good crystallinity, the metal sites are confined in the crystalline frameworks and blocked by the organic linkers, which is not good for electrocatalysis. In this regard, low-crystalline bimetallic MOFs with highly exposed active sites and porous structures hold great promise for electrocatalysis. Mai and co-workers reported the synthesis of low-crystalline bimetallic Fe/Ni-MOF NPs (Fe_xNi_y-BDC) for the OER.¹⁶⁴ The addition of Ni precursors in the synthesis solution of Fe-BDC (Fe-MIL-88B) caused mismatched coordination with organic linkers, thus resulting in the loss of the long-range ordered structure and formation of rich defects (Fig. 13C). Fe₁Ni₂-BDC showed a small overpotential of 260 mV at a current density of 10 mA cm⁻² and a high Faradaic efficiency (FE) of 99.5% for the OER in 1.0 M KOH. The superior catalytic performance of Fe₁Ni₂-BDC could be attributed to the exposed active sites, synergistic effect between Fe and Ni, and fast charge transfer in

Chemical Science

the amorphous structure.

The integration of bimetallic MOFs with functional materials can enhance the characteristics of MOFs with improved electrical conductivity, chemical stability and mechanical strength for electrocatalytic applications.^{6,167,178–180} Lu and coworkers reported the in situ growth of amino-functionalized bimetallic NH₂-MIL-88B(Fe₂Ni) (NFN-MOF) on 3D microporous nickel foam (NF) as an efficient bifunctional electrocatalyst for overall water splitting.181 In a 1.0 M KOH electrolyte, the synthesized NFN-MOF/NF exhibited overpotentials of 240 and 87 mV at a current density of 10 mA cm⁻² for the OER and HER, respectively. For the overall water splitting with NFN-MOF/NF as both the anode and cathode, a cell voltage of only 1.56 V was required to achieve a current density of 10 mA cm⁻². The excellent catalytic performance of NFN-MOF/NF can be attributed to the synergistic effect between Ni and Fe metal ions in the MOF, and a positive coupling effect between the MOF and NF.

3.3 Energy storage and conversion

MOFs with large surface areas, adjustable pore structures, and redox metal centres are promising electrode materials for electrochemical capacitors and rechargeable batteries. 14,182-186 However, the inherent poor electrical conductivity of MOFs is one of the greatest obstacles to achieve high performance in capacitors. In bimetallic MOFs, the electrochemical properties can be tuned by mixing two different metals in the SBUs. Bimetallic MOFs with enhanced electrical conductivity have been applied as the electrode materials for supercapacitors. 187-193 Pei, Chen and co-workers improved the electrical conductivity of MOFs by partially exchanging Ni²⁺ in the Ni-MOF ([Ni₃(OH)₂(tp)₂(H₂O)₄]· $2H_2O$, tp = $C_8H_4O_4^{2-}$) with Co^{2+} or Zn^{2+} for hybrid supercapacitors. 190 The specific capacities of Co/Ni-MOF, Zn/Ni-MOF and Ni-MOF were 236.1, 161.5 and 142.3 mA h g^{-1} at 1 A g^{-1} , with a capacity retention of 82.8%, 56% and 37% at 10 A g^{-1} , respectively (Fig. 14A). The assembled hybrid supercapacitors (Co/Ni-MOF//CNTs-COOH) exhibited an energy density of 49.5 W h kg⁻¹ and a power density of 1450 W kg⁻¹. The metal ion exchange resulted in an increase of free holes and the interlayer distance and in turn led to an enhancement of the electrical

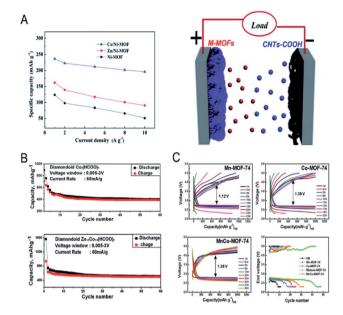


Fig. 14 (A) Specific capacity of pristine Ni-MOF, Zn/Ni-MOF and Co/Ni-MOF at various current densities (left). An abstract illustration of hybrid supercapacitors containing M-MOFs and CNTs-COOHs as a positive and negative electrode, respectively (right). Reproduced with permission from ref. 190. Copyright 2017, Royal Society of Chemistry. (B) Capacity vs. cycle number plot for FOR3 (top) and FOR4 (bottom) (current density of 60 mA g $^{-1}$, potential window 0.005–3 V, recorded at room temperature). Reproduced with permission from ref. 195. Copyright 2010, Royal Society of Chemistry. (C) Galvanostatic cycling performance of Li-O2 batteries using Mn-MOF-74, Co-MOF-74, and MnCo-MOF-74 electrodes at a limited capacity of 1000 mA h g $^{-1}$ with a current density of 200 mA g $^{-1}$. End voltage vs. cycle number of the electrodes. Reproduced with permission from ref. 198. Copyright 2018, American Chemical Society.

conductivity and surface area, explaining the enhanced performance of bimetallic MOFs for capacitors.

Bimetallic MOFs have been investigated as anode and cathode materials for lithium-ion batteries (LIBs). When using bimetallic MOFs as anode materials, the adjustable pores can allow Li ions to be stored and reversibly inserted/extracted, leading to insertion-type electrodes. 194 Some bimetallic MOFs enabling reversible transformation/regeneration can be employed as conversion-type electrodes. 195 For example, Vittal et al. investigated the electrochemical performance of FOR4 (Zn_{1.5}Co_{1.5}(HCOO)₆). The formate-bridged MOFs were converted to lithium formate MOFs upon lithiation and regenerated upon de-lithiation. The reversible conversion reaction led to good cycling stability of FOR4 (Fig. 14B), with a high reversible capacity of 510 mA h g⁻¹ up to 60 cycles at 60 mA g^{-1} , exceeding that of monometallic CoMOF (FOR3). As cathodes in LIBs, bimetallic MOFs with redox metal centres and good Li-ion mobility within the solid are good candidates, such as $K_{0.14}Mn_{1.43}[Fe(CN)_6]\cdot 6H_2O^{196}$ and $K_{0.1}Ni[Fe(CN)_6]_{0.7}$ $[Fe(CN)_6]_{0.3} \cdot 4.7 H_2O.^{197}$

Bimetallic MOFs can be applied as cathode materials for lithium-oxygen batteries (LOBs). The porous structures and tuneable bimetallic active sites endow bimetallic MOFs with the Perspective Chemical Science

capabilities to optimize the performance. Lee and co-workers used bimetallic MnCo-MOF-74 materials as cathode catalysts for Li–O $_2$ batteries. 198 MnCo-MOF-74 delivered a discharge capacity of 11 150 mA h g $^{-1}$ and excellent cyclability (44 cycles) with a low overpotential at a limited capacity of 1000 mA h g $^{-1}$, outperforming the monometallic counterparts, Mn- and Co-MOF-74 (Fig. 14C). The synergistic integration of Mn- and Co-metal clusters contributed to the improved efficiency and reversibility.

3.4 Luminescence sensing

Luminescent MOFs (LMOFs) are an important sub-category of MOFs. ¹⁹⁹ Lanthanide (Ln) cations are particularly attractive for the construction of LMOFs because of their characteristic sharp emission bands and high quantum yields in the near-infrared and visible regions. Typically, Eu³⁺ and Tb³⁺ are usually used in LnMOFs because of their strong characteristic red emission at 614 nm ($^5D_0 \rightarrow ^7F_2$) and green emission at 541 nm ($^5D_4 \rightarrow ^7F_5$), respectively.

Mixed Ln3+ ions with different emissions can be integrated into a MOF framework to tune the luminescence properties.²⁰⁰ Moreover, the metal distribution (solid solution or core-shell) in mixed LnMOFs influences the luminescence properties. Mahon, Burrows and co-workers studied the effect of metal distribution on the luminescence properties of mixed LnMOFs.²⁰¹ Solid solution mixed LnMOFs, [Gd_{0.17}Tb_{0.19}Eu_{0.64}(-Hodip) (H_2O)]· nH_2O $(H_4odip = 5.5'-oxydiisophthalic acid),$ showed an emission spectrum with strong bands of Eu3+ and weak bands of Tb3+ and H4odip. This is due to the energy transfer from Tb³⁺ to Eu³⁺, resulting in a quenching of Tb³⁺ transitions. Core-shell mixed LnMOFs displayed different emission spectra because the metal energy transfer between Ln³⁺ ions was prevented. Gd@Tb@Eu and Tb@Eu@Gd showed emission spectra dominated by Tb3+ emissions with lower intensity Eu³⁺ and ligand transitions. Eu@Gd@Tb exhibited an emission spectrum with only Eu³⁺ and ligand transitions present. In all the core-shell structures, the core Ln³⁺ emissions were not observable. Therefore, alteration of shell ordering and

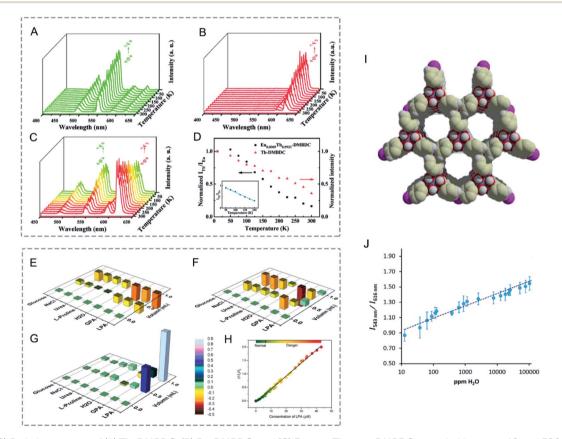


Fig. 15 (A–C) Emission spectra of (A) Tb-DMBDC, (B) Eu-DMBDC, and (C) $Eu_{0.0069}Tb_{0.9931}$ -DMBDC recorded between 10 and 300 K (excited at 355 nm from the third harmonic of a Nd:YAG laser). (D) Temperature dependence of the integrated intensity ratio of Tb^{3+} (545 nm) for $Eu_{0.0069}Tb_{0.9931}$ -DMBDC (black squares), and temperature dependence of the integrated intensity of Tb^{3+} (545 nm) for Tb-DMBDC (red triangles). (Inset) Fitted curves of the integrated intensity ratio for $Eu_{0.0069}Tb_{0.9931}$ -DMBDC from 50 to 200 K. Reproduced with permission from ref. 206. Copyright 2012, American Chemical Society. (E–G) Relative luminescence intensity changes of (E) Tb-ZMOF, (F) Eu-ZMOF, and (G) MZMOF-3 in the presence of different analytes. The intensity change is indicated by the colormap from -0.5 to 0.9. (H) Integrated luminescence intensity changes of MZMOF-3 suspended in MeOH toward 0.03, 0.10, and 0.13 mM LPA. Reproduced with permission from ref. 207. Copyright 2015, American Chemical Society. (I) Chemical Structure of PCM-22. (J) Relative photoemission response ratios obtained upon addition of trace H_2O to Eu_1 : Tb_5 -PCM-22 pre-soaked in D_2O showing a linear response. Error bars were obtained from three separate experiments. Reproduced with permission from ref. 208. Copyright 2017, Elsevier.

Chemical Science

thickness could tailor the luminescence properties of core-shell

A variety of bimetallic LnMOFs have acted as ratiometric sensors with high sensitivity and high selectivity toward ionic species, pH, temperature, environmental toxins, explosives, biomolecules, etc. 202-204

Bimetallic LnMOFs with dual emissions can be employed as self-referencing luminescence thermometers based on the intensity ratios of two separate transitions.205 Qian, Chen and co-workers reported luminescent mixed Ln-MOFs, $(Eu_xTb_{1-x})_2(DMBDC)_3(H_2O)_4 \cdot DMF \cdot H_2O$ $(Eu_rTb_{1-r}-DMBDC,$ DMBDC = 2,5-dimethoxy-1,4-benzenedicarboxylate, x = 0.0011, 0.0046, and 0.0069) as luminescent thermometers. 206 From 10 to 300 K, the luminescence intensity of Tb3+ at 545 nm in Tb-DMBDC and Eu³⁺ at 613 nm in Eu-DMBDC both decreased gradually as the temperature increases (Fig. 15A and B). The mixed lanthanide MOFs exhibited a significantly different temperature-dependent luminescence behaviour. Eu_{0.0069}Tb_{0.9931}-DMBDC, the emission intensity of Tb³⁺ decreased, while that of Eu3+ increased with the increase of temperature (Fig. 15C). The emission intensity ratio $(I_{\rm Tb}/I_{\rm Eu})$ correlated well with the temperature in the range of 50 to 200 K (Fig. 15D). Moreover, Eu_{0.0069}Tb_{0.9931}-DMBDC emitted temperature dependent luminescence colours from green-yellow to red at temperatures ranging from 10 to 300 K. The exhibited temperature-dependent emissions and luminescence colours in Eu/Tb-DMBDC may be attributed to the temperature-dependent energy transfer from Tb³⁺ to Eu³⁺ ions.

Shi, Zaworotko and co-workers synthesized mixed Ln zeolitelike MOFs (Ln-ZMOFs), Eu_xTb_{1-x} -ZMOF, as a fluorescent indicator for lysophosphatidic acid (LPA), a cancer biomarker.207 In $Eu_{0.6059}Tb_{0.3941}$ -ZMOF (MZMOF-3), the integrated intensity ratio of Eu³⁺ and Tb³⁺ (I_{Eu}/I_{Tb}) correlated well with the concentration of LPA in MeOH (Fig. 15H). Moreover, MZMOF-3 exhibited selective detection for LPA over additives (water, glucose, Na⁺, Cl⁻, proline, and urea). For MZMOF-3, the luminescence intensity of LPA was 10-80 times higher than those of the additives (Fig. 15G). However, Tb-ZMOF and Eu-ZMOF exhibited similar fluorescence emission signals towards additives and LPA (Fig. 15E and F).

Mixed Ln-MOFs have also been studied as sensors for quantitative detection of water and identification of solvents. Humphrey and co-workers synthesized mixed-metal PCM-22 with controlled amounts of Eu3+, Gd3+ and Tb3+ as sensors for the identification of a wide range of solvents, and especially for trace H₂O detection in D₂O (Fig. 15I and J).²⁰⁸ PCM-22, with a formula of [Ln(tctp) (OH₂)₃]·3(1,4-dioxane), was synthesized by the reaction of $Ln(NO_3)_3$ with $P(C_6H_4-p-CO_2H)_3$ (tctpH₃). For binary Eu₁: Tb₁-PCM-22, based on the emissions of Tb³⁺ (616 nm) and Eu³⁺ (543 nm), the ratio of I_{543}/I_{616} showed a linear relationship with H₂O concentration in D₂O over the range of 10-120 000 ppm. For ternary PCM-22 with four Eu: Gd: Tb compositions, they provided a unique "eight-factor" fingerprint for rapid identification of 18 solvents.

In conclusion, due to the synergistic effect between the two metals, bimetallic MOFs can exhibit significantly enhanced physical and chemical features compared with their monometallic counterparts. Therefore, through the rational design of bimetallic MOFs, they can afford excellent performance in gas adsorption, catalysis, energy storage and conversion, luminescence sensing, and so on.

Synthesis of bimetallic MOF derivatives

Since the MOF pyrolysis was reported by Xu and co-workers for porous carbon synthesis in 2008209 and for metal oxide synthesis in 2010,210 MOF derivatives have been intensively designed and synthesized. 33,211 Especially, bimetallic MOFs with controllable compositions in the SBUs provide a promising platform for the preparation of a variety of functional materials, such as carbon composites (carbon supported atomically dispersed metals, metal NPs, alloy, oxides, carbides, sulphides, and phosphides), metal compounds (oxides, hydroxides, nitrides, sulphides, and phosphides), and MOF composites, which have a wide variety of physicochemical properties and applications.

4.1 Carbon composites

The pyrolysis of MOFs has been adopted as an effective way to obtain carbon composites with various morphologies and compositions. The texture and graphitization degree of carbon supports have a great influence on the performance of the composites. Carbon supports with a high surface area and hierarchical pores can guarantee the free diffusion of substrates.212 Graphitized carbon can enhance electrical conductivity and chemical and thermal stability.

ZIFs have been widely investigated as precursors to synthesize carbon-based materials. The pyrolysis of bimetallic ZIFs can realize well-graphitized carbons, high-surface-area carbons, and active metal-N_r-C sites at the same time, which cannot be achieved by monometallic ZIFs. For example, the pyrolysis of Zn-based ZIF-8 can afford high-surface-area carbon with high N contents but fail to provide active metal-N_x-C sites and wellgraphitized carbon. 213,214 On the other hand, the pyrolysis of Cobased ZIF-67 can give well-graphitized carbon and highly active Co-N_x-C sites but only offer carbon with a low surface area and porosity.215-217 In this regard, Xiong, Jiang and co-workers employed a series of bimetallic ZIFs (BMZIFs-n, n represents the ratio of Zn/Co) as precursors to afford Co, N-doped porous carbons (CNCo-n) with a large surface area, high graphitization degree, and highly dispersed N and CoN_r active species (Fig. 16A).218 BMZIFs-n were pyrolyzed at 900 °C under N2, during which the generated ZnO was reduced by carbon and then evaporated. After treating the calcined products in H₂SO₄ at 80 °C to remove the inactive and unstable Co species, CNCo-n could be afforded. The BET surface areas of CNCo-n (n = 0, 0.2,5, 10, 20, 40, and 100) were 270, 362, 550, 1090, 1225, 1480, and 2184 m² g⁻¹, respectively. Besides, Yamauchi and co-workers thermally transformed core-shell ZIF-8@ZIF-67 into nanoporous nitrogen-doped carbon@graphitic carbon (NC@GC) materials.99 ZIF-8@ZIF-67(x) (x represents the molar ratio of Co²⁺/Zn²⁺) materials were thermally treated at 800 °C under a N₂

B

| Description | Description

Fig. 16 (A) Schematic illustration for the preparation of porous carbons from BMZIFs. Reproduced with permission from ref. 218. Copyright 2015, Wiley-VCH. (B) Schematic illustration of the construction of the nature-inspired hydrangea-like superstructure of open carbon cages $\it via$ morphology-controlled thermal transformation of core@shell MOFs. Reproduced with permission from ref. 219. Copyright 2019, Wiley-VCH. (C) The effect of reduction potential of metal atoms present in the MOFs on the formation of metal/metal oxide nanoparticles. Metals having a reduction potential above -0.27 V undergo thermolysis in an N_2 atmosphere to give pure metal nanoparticles, whereas metals with a reduction potential less than -0.27 V, even in an N_2 atmosphere, produce metal oxides only. Reproduced with permission from ref. 223. Copyright 2012, Royal Society of Chemistry. (D) The formation of Co SAs/N-C. Reproduced with permission from ref. 236. Copyright 2016, Wiley-VCH.

flow, followed by washing with HF solution to remove the residual Zn and unstable Co species. The obtained NC@GC samples showed intermediate surface areas between those of NC and GC derived from ZIF-8 and ZIF-67, respectively. In addition, NC@GC showed mesopores on the particle surface and abundant layered graphitic carbon structures, which were similar to those of GC.

Recently, Xu and co-workers reported that introducing guest Fe ions into a ZIF-8@ZIF-67 precursor led to the self-assembly of open carbon cages into a hydrangea-like 3D superstructure (Fig. 16B).²¹⁹ Direct pyrolysis of core-shell ZIF-8@ZIF-67 produced isolated open-wall N-doped carbon cages with insufficient contact and total conductivity. The introduction of guest Fe ions into the MOF precursor formed FeCo alloy NPs during the pyrolysis, which could catalyse the growth of carbon nanotubes and thus interconnect neighbouring cages to form a hydrangea-like 3D superstructure.

The employment of bimetallic MOFs as precursors can afford precise size, composition, and structure control of the supported metal/oxide NPs. $^{220-222}$ This is benefited from the ability to control the compositions and distributions of metal ions in MOFs, which are not achievable by other synthetic methods. The calcination of bimetallic MOFs under an inert atmosphere can afford metal alloy or oxide NPs depending on the reduction potential of the metal ions. 223 Metal ions (*e.g.*, 24 Cu²⁺ and 24) with a reduction potential of 22 V or higher usually form metal NPs after calcination under an inert atmosphere, whereas metal ions (*e.g.*, 24 and 24) with reduction potentials lower than 24 V form metal oxide NPs (Fig. 16C). For example, Chen and co-workers calcined bimetallic MOFs

 $(\text{Fe}_3[\text{Co}(\text{CN})_6]_2)$ at 600 °C in N₂, affording FeCo alloy NPs encapsulated in N-doped graphene layers.²²⁰ Gao, Lou and coworkers pyrolyzed Co/Mn-MIL-100 at 800 °C in a 5% H₂/Ar atmosphere, affording a MnO/Co hybrid supported by porous graphitic carbon.²²⁴

The type of metal compound generated from the pyrolysis of bimetallic MOFs can be affected by the elements in the ligands. Carbon atoms can diffuse into the interstices of metal atoms to form bimetallic carbides. For example, Su and co-workers reported the synthesis of Co/Mo $_2$ C/Mo $_3$ Co $_3$ C@C and Ni/Mo $_2$ C@C derived from two bimetallic MOFs (CoMo-MOF and NiMo-MOF) annealed at 900 °C in N $_2$, respectively. The metal compounds (metal nitrides, phosphides and sulphides) supported on carbon materials can also be synthesized from bimetallic MOFs if suitable ligands with heteroatoms are employed.

Bimetal nitrides, phosphides and sulphides embedded in carbon can also be obtained through introducing additional precursors (N/P/S-containing regents) before²²⁸⁻²³¹ or after the pyrolysis process.^{94,232-235} Moreover, additional metal precursors can be introduced into MOFs before calcination to alter the composition of metal compounds.

The pyrolysis of MOFs serves as an ideal route for preparing various metal single atoms (SAs) on porous carbon (SAs/C). Delicate control is required to avoid the conversion of metal ions into aggregated NPs at high temperature. Bimetallic MOFs offer a promising platform for the synthesis of SAs/C based on the idea of using a second metal that is easily removed after pyrolysis to extend the distance between adjacent targeted metals to avoid aggregation during pyrolysis.236-240 Wu, Li and co-workers demonstrated the concept for the synthesis of Co SAs on N-doped porous carbon (Co SAs/N-C) through the pyrolysis of a bimetallic Zn/Co MOF (Zn/Co-BMOF).236 The addition of Zn2+ could dilute the concentration of Co2+ and extend the adjacent distances between Co atoms. During the pyrolysis process, Zn was evaporated at high temperature, leaving abundant N sites to anchor and stabilize the isolated Co atoms (Fig. 16D). Co SAs/N-C obtained by calcination at 800 and 900 °C showed a 4 and 2 metal coordination number with surrounding N atoms, respectively. Further increasing the calcination temperature to 1000 °C broke the Co-N bonds and caused the formation of Co NPs. In the sequent work, Wu, Li and co-workers synthesized Fe-Co dual sites embedded on Ndoped porous carbon [(Fe,Co)/N-C] derived from Zn/Co-BMOF encapsulated FeCl3.241 FeCl3 was immobilized within the pores of Zn/Co-BMOF by a double-solvent method. During the calcination, Fe salts were reduced by carbon and bonded with neighbouring Co atoms to form Fe-Co dual-sites. The Fe species would accelerate the decomposition of MOFs and force the generation of voids inside the N-C support.

4.2 Metal compounds

The thermal calcination of bimetallic MOFs in air can lead to their decomposition into their corresponding bimetallic oxides. To achieve a higher surface area and porosity and preserve the original structure of parent MOFs to a certain extent, a two-step annealing (first in N_2 and then in air) can be applied to synthesize metal oxide nanostructures. The use of bimetallic MOFs as precursors to obtain bimetallic oxides has emerged as a powerful synthetic route, offering the possibility to precisely control the compositions and structures of metal oxides.

The achieved success in the control of metal distribution in MOFs can allow the tuning of the composition of the obtained metal oxides.242-245 Zhou and co-workers synthesized Zn_x- $Co_{3-x}O_4$ (0 < $x \le 1$) hollow polyhedra through calcination of bimetallic Zn-Co-ZIFs.242 Bimetallic Zn-Co-ZIFs were first heated in N2 and then in air at 400 °C. The first thermal treatment in N2 was of vital importance to partially preserve the porous structure of ZIFs. Monge, Gándara and co-workers demonstrated the control of the composition of multimetal oxides through the use of MOFs constructed from up to four different metal elements (Fig. 17A).244 Multimetallic MOFs, constructed from a helical inorganic SBU with different cations (Zn²⁺, Co²⁺, Mn²⁺, and Ca²⁺) and an organic linker H₂hfipbb [4,4'-(hexafluoroisopropylidene)bis-(benzoic acid)], were subjected to a thermal treatment in air at 800 °C to obtain the corresponding multimetal oxides. The metal arrangements and

ratios of MOFs could be translated to metal oxides after calcination.

Metal oxides with complex structures can be fabricated from rationally designed bimetallic MOF precursors. 246,247 Song, Lou and co-workers reported the preparation of ${\rm Co_3O_4/Co}$ -Fe oxide double-shelled nanoboxes (DSNBs) derived from ZIF-67/Co–Fe PBA yolk–shell nanocubes (YSNCs). 248 ZIF-67/Co–Fe PBA YSNCs were fabricated through an anion-exchange reaction between ZIF-67 and ${\rm [Fe(CN)_6]^{3-}}$ ions. The ZIF-67/Co–Fe PBA YSNCs were further converted to ${\rm Co_3O_4/Co}$ -Fe oxide DSNBs by calcination in air (Fig. 17B).

Metal hydroxides can be fabricated from bimetallic MOF precursors through alkali hydrolysis. ²⁴⁹⁻²⁵² Zou, Liu and coworkers reported the synthesis of bimetallic double hydroxides (MDHs) derived from bimetallic NiCo-MOF-74 through an alkaline treatment (Fig. 17C). ²⁵⁰ Ni/Co MOF-74 samples were dispersed in a 2 M KOH aqueous solution under stirring at room temperature, followed by hydrothermal treatment at 120 °C for 2 h. The hydrothermal treatment with KOH resulted in the destruction of micron-sized MOF-74 and the formation of nanoscale MDH.

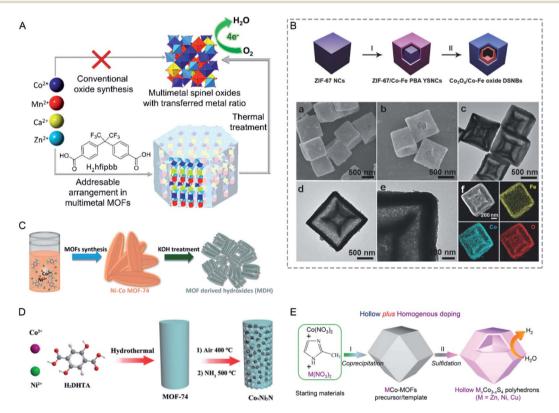


Fig. 17 (A) Thermal decomposition of multimetal MOFs allows the obtaining of multication oxides with compositions not attainable with conventional oxide synthetic routes. The metal ratios in the resulting oxides are transferred from their corresponding parent MOFs. Reproduced with permission from ref. 244. Copyright 2019, American Chemical Society. (B) Schematic illustration of the formation process of Co_3O_4/Co –Fe oxide DSNBs: (I) ion–exchange reaction between ZIF-67 NCs and $[Fe(CN)_6]^3$ —ions to form ZIF-67/Co–Fe PBA YSNCs and (II) subsequent conversion to Co_3O_4/Co –Fe oxide DSNBs by thermal annealing (top). (a, c) FESEM and (b, d–f) TEM images of (a, b) ZIF-67 NCs and (c–f) ZIF-67/Co–Fe PBA YSNCs. Reproduced with permission from ref. 248. Copyright 2018, Wiley-VCH. (C) Illustration of the synthesis process from MOF-74 to Ni–Co MDH. Reproduced with permission from ref. 250. Copyright 2017, American Chemical Society. (D) Schematic diagram of synthesis for porous Co_xNi_yN composites. Reproduced with permission from ref. 253. Copyright 2019, American Chemical Society. (E) Schematic illustration of fabrication of hollow Co-based bimetallic sulphides. Reproduced with permission from ref. 254. Copyright 2016, American Chemical Society.

Bimetallic nitrides can be prepared from bimetallic MOFs through nitridation under an NH₃ atmosphere. Guo and coworkers synthesized bimetallic CoNi nitrides derived from bimetallic CoNi-MOF-74.²⁵³ CoNi-MOF-74 was first converted to Ni₁Co₂O₄ through calcination at 400 °C in air, and then transformed into Co₂Ni₁N by nitridation under an NH₃ atmosphere at 500 °C (Fig. 17D). The resulting metal nitrides inherited the morphology from their corresponding precursors.

Bimetallic sulphides can be synthesized using bimetallic MOFs as templates via a hydrothermal sulfidation reaction. 193,254-256 Zou and co-workers reported the synthesis of hollow bimetallic sulphides ($M_xCo_{3-x}S_4$, M = Zn, Ni, and Cu) by solvothermal sulfidation and thermal annealing from Co-based bimetallic MOFs.²⁵⁴ MCo-MOFs (M = Zn, Ni, and Cu) were treated in an ethanol solution of thioacetamide (TAA) at 120 °C for 4 h, followed by calcination under a N₂ atmosphere at 350 °C for 2 h (Fig. 17E). The obtained M_xCo_{3-x}S₄ preserved the rhombic dodecahedral morphology of MOF precursors, while formed a hollow structure after the sulfidation procedure. S²⁻ ions released from TAA first reacted with metal ions on the MOF surface to form a thin layer of sulphides, which could promote the outward diffusion of metal ions against the inward diffusion of S²⁻ ions. Then the inner framework was gradually dissolved and released metal ions to react with S2- ions on the outer surface, which finally led to the generation of a hollow void inside the shell.

Transition metal phosphides (TMPs) show extremely low cost and expected long-term stability in both acidic and alkaline operating environments. Bimetallic MOFs have been applied for the synthesis of TMPs. $^{257-262}$ Zhao and co-workers synthesized nickel–cobalt mixed metal phosphide nanotubes ($\rm Co_xNi_yP,\ x$ and y represent the molar ratios of Co and Ni in the MOF precursor, respectively) derived from bimetallic CoNi-MOF-74. 258 Bimetallic MOF-74 materials with different Co/Ni ratios were first calcined at 350 °C in air to afford $\rm Co_xNi_yO$, followed by phosphorization with NaH₂PO₂ at 300 °C in N₂ to afford $\rm Co_xNi_yP$.

As summarized above, various types of metal compounds can be obtained through the treatment of bimetallic MOFs.

4.3 MOF composites

Complete decomposition of MOFs usually leads to a dramatic decrease of the surface area and loss of well-defined pore structures. 209,213 Recently, Xu and co-workers have demonstrated a new concept of "quasi-MOFs" fabricated through controlled deligandation of MOFs, which can realize both a porous structure and exposed inorganic nodes. 263 This controlled thermal transformation method has been successfully applied on solid solution bi- and multi-metallic MOFs for the synthesis of MOF immobilized metal NPs or oxides. 264,265 This design takes advantage of different coordination abilities of the metal ions with the organic linkers. The metal ions with weaker coordination with the organic linkers transform into metal NPs/compounds under certain conditions while the other metal ions remain coordinated with the organic linkers to preserve the framework. Hu and co-workers reported a thermal

transformation of a benzimidazole-modified Cu/Co bimetal-MOF into a Cu-nanowire@quasi-MOF composite (Fig. 18A). 264 The Cu/Co bimetal-MOF was calcined at 300 °C for 30 min under a $\rm N_2$ atmosphere to afford a quasi-MOF matrix with a partially preserved MOF structure embedded with Cu nanowires. Under similar calcination conditions, monometallic Cu-MOF transformed into core–shell Cu_2O@N doped carbon composites. During the calcination process, Cu-ligand bonds with weaker coordination would break and form metastable Cu NPs, while the Co-MOF part with higher stability would serve as a morphology retainer and a nano-channel template to reassemble Cu NPs into Cu nanowires.

Besides thermal transformation, solvent induced transformation is also a powerful strategy for the conversion of bimetallic MOFs to composites of MOFs and metal compounds. Luo and co-workers obtained $\rm Zn_{1-x}Co_x\text{-}ZIF@Zn_{1-x}Co_xO$ through the transformation of $\rm Zn_{1-x}Co_x\text{-}ZIF$ with AgNO₃ (Fig. 18B). 266 Zn_{1-x}Co_x-ZIF was dispersed in an aqueous solution of silver nitrate (AgNO₃) and stirred for 1 h to obtain Zn_{1-x}Co_x-ZIF@Zn_{1-x}Co_xO. AgNO₃ acted as the catalyst to break the coordinative bonds of MOFs and created a hydroxyl rich environment for the formation of Zn_{1-x}Co_xO on the surface of Zn_{1-x}Co_x-ZIF.

Selectively removing the core MOFs in single- or multicore-shell bimetallic MOFs can obtain hierarchical-pore or hollow MOF immobilized metal compound composites. In this design, less stable MOFs act as seeds to grow stable MOFs as the shell, followed by selective removal of the core MOFs to generate pores. The generated mesopores/macropores can facilitate the diffusion of substrates and the desorption of products.

For example, Li, Zhong and co-workers used MOF-5 as a template to grow UiO-66(Zr), followed by the removal of the cores to synthesize hierarchical UiO-66(Zr) (H-UiO-66).267 MOF-5 is stable in certain solvents but sensitive towards moisture and acid, while UiO-66(Zr) is stable even in acidic solutions. Nanosized MOF-5 particles were first synthesized, followed by the growth of UiO-66(Zr). The obtained material was washed with acid aqueous solution to get the targeted material H-UiO-66(Zr) with Zr species anchoring in the mesopore surface (Fig. 18C). In another system, Wu, Li, and co-workers reported a mild phase transformation of core-shell ZIF-67@ZIF-8 structures into hollow Zn/Co ZIF particles.268 They treated core-shell ZIF-67@ZIF-8 with Co2+ in methanol at 120 °C for 4 h, resulting in the dissolution of the solid interior and then the formation of a hollow structure with interlaced nanoplates (Fig. 18D). The authors proposed that methanol molecules formed H-bonds in the presence of Co²⁺ to break the coordination bonds between Co²⁺ and 2-MeIm, driving the structural evolution of ZIF-67. Muhler, Fischer and co-workers reported similar results in parallel.269 During the epitaxial growth of ZIF-8 on preformed ZIF-67 under solvothermal conditions, ZIF-67 partially dissolved to release cobalt ions to form cobalt hydroxide with a sheet-like structure.

Carbon composites, metal compounds and MOF composites can be derived from bimetallic MOFs through pyrolysis, hydrothermal treatment, and so on. This wide variety of MOF- Α В

Fig. 18 (A) Scheme and TEM images of Cu MOF(300), Cu/Ni bimetal-MOF(300), and Cu-nanowire@Quasi-MOF. Reproduced with permission from ref. 264. Copyright 2019, Royal Society of Chemistry. (B) Synthetic procedure of the Zn_{1-x}Co_x-ZIF@Zn_{1-x}Co_xO hybrid photocatalyst. Reproduced with permission from ref. 266. Copyright 2018, Royal Society of Chemistry. (C) In situ self-assembly of MOA through the reaction between a metal ion and organic ligand. MOA@H-MOF composite formed by a one-pot self-assembly reaction. H-MOF formed through removing the MOA template. Reproduced with permission from ref. 267. Copyright 2015, Nature Publishing Group. (D) Ilustration of the structural evolution (top). TEM image, SEM image, and EDX mappings of H-Zn/Co-ZIF (bottom). Reproduced with permission from ref. 268. Copyright 2015, Wiley-VCH.

derived materials can be applied in many applications, which will be introduced in the following section.

Applications of bimetallic MOF derivatives

The applications of the majority of bimetallic MOFs are restricted by their low stability, poor conductivity and blockage of active sites. Bimetallic MOF-derived materials show high stability, high conductivity, and exposed active sites. These properties provide bimetallic MOF derivatives with more opportunities for applications in catalysis under harsh conditions and electrochemical energy storage and conversion.

5.1 Catalysis

Chemical Science

5.1.1 Organocatalysis. Diverse MOF-derived porous materials are very promising for various organic reactions, including oxidation, dehydrogenation, reduction, and biomass transformation.

MOF-derived materials are active for many reduction reactions, such as the hydrogenation of phenol, 270 nitro compounds^{271,272} and nitriles,²²¹ and the reduction of NO^{273,274} and CO2.275 As an example, Li and co-workers applied bimetallic alloy NPs embedded in an N-doped carbon matrix (M-M'@C-N, M/M' = Co, Ni, Cu) derived from bimetallic MOFs (M-M'(1,4 $bdc)_2(dabco) \cdot 4DMF \cdot 1/2H_2O, M/M' = Co, Ni, Cu)$ for transfer hydrogenation of nitriles to imines.221 In the hydrogenation of benzonitrile to the corresponding imine, Co-Ni(3:1)@C-N exhibited remarkable activity with over 98% yield for the desired product after 15 h, which was 5 times and 7 times as high as that of Ni@C-N and Co@C-N, respectively (Fig. 19A). Co-Ni@C-N with a Co-Ni molar ratio of 3:1 showed the highest activity;

further decreasing or increasing the proportion of Co resulted in a decrease of activity.

Bimetallic MOF-derived porous catalysts have also been developed for a variety of oxidation reactions, such as the oxidation of alcohols, 271,276,277 acetone, olefin and toluene, 278 and organic pollutant degradation. 279,280 As an example, Han, Yeung and co-workers prepared a binary metal oxide (CeCuOx) derived from bimetallic MOFs (CeCuBDC) as the catalyst for the oxidation of organic compounds.278 In the oxidation of toluene to CO_2 , $CeCuO_x$ exhibited high catalytic activity, with a T_{50} (temperature required for 50% conversion) and T_{90} of 150 and 186 °C, respectively (Fig. 19B). CeCuO_x showed lower activation energy (52.4 kJ mol⁻¹) than CeO_2 (57.5 kJ mol⁻¹) and CuO (70.5 kJ mol⁻¹). The CeCuO_x catalyst was also highly active for the oxidation of methanol, acetone and o-xylene, with a T_{50} of 80, 87 and 142 °C, respectively.

Controlled generation of hydrogen from chemical hydrogen storage materials is of vital importance to the hydrogeneconomy paradigm in the future.²⁸¹⁻²⁸⁴ Bimetallic MOF-derived nanomaterials exhibit high catalytic performance for the release of hydrogen from chemical hydrogen storage materials such as ammonia borane (NH3BH3, AB) and lithium borohydride (LiBH₄).²⁸⁵⁻²⁸⁸ Chen and co-workers fabricated porous cobalt phosphide supported by carbon-based nanoframeworks (CoP@CNFs), which was derived from Zn/Co-ZIF and was applied for hydrogen generation from AB.286 Zn/Co-ZIF was calcined in air to get Zn-Co-O@CNF, followed by phosphidation using Na₂H₂PO₂ and further acid treatment to get CoP@CNFs. CoP@CNFs gave an initial TOF value of 165.5 $\text{mol}_{\text{H}_2} \text{ mol}_{\text{metal}}^{-1} \text{ min}^{-1}$ at 298 K, maintaining 90% of its initial activity after 4 cycles.

Biomass has been an important resource for the production of chemicals, fuels, and energy.289 Bimetallic MOF-derived

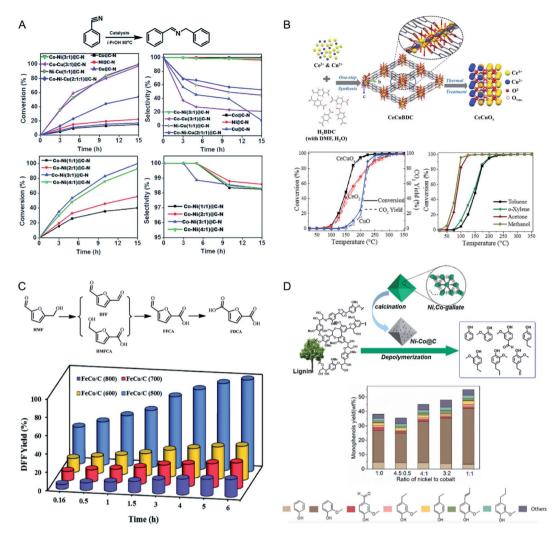


Fig. 19 (A) The conversion of benzonitrile and selectivity of the corresponding imine with various catalysts for the transfer hydrogenation of benzonitrile. Reaction conditions: 0.5 mmol nitriles, 4 mL i-PrOH, catalyst (metal 10 mol%), 80 °C, and 15 h. Reproduced with permission from ref. 221. Copyright 2016, Royal Society of Chemistry. (B) Schematic diagram of the synthesis procedure of the bimetallic MOF-derived CeCuO_x catalyst (top). Toluene conversion and CO_2 yield versus temperature curves over CeO_2 , CuO, and $CeCuO_x$ catalysts (left bottom). Conversion versus temperature curves for complete oxidation of methanol, acetone, toluene, and o-xylene over the $CeCuO_x$ catalyst. (Note: [VOC] = 500ppm, $m_{\text{catalyst}} = 0.15 \text{ g}$, and gas hourly space velocity (GHSV) = 23 000 h⁻¹) (right bottom). Reproduced with permission from ref. 278. Copyright 2019, Wiley-VCH. (C) Products of HMF oxidation (top). DFF yield as a function of reaction time over the FeCo/C catalysts. Reaction conditions: 1 $^{\circ}$ mmol HMF, catalyst (metal 20 mol%), $^{\circ}$ Na₂CO₃ 1 mmol, 2 mL toluene, 1 MPa O₂, 100 °C, and 6 h (bottom). Reproduced with permission from ref. 290. Copyright 2016, Royal Society of Chemistry. (D) Depolymerization of renewable lignin extracted from poplar to monophenolic compounds with the Ni-Co@C catalyst was prepared from MOFs (top). Monophenol yield on the Ni_xCo_{1-x}/C catalyst (bottom). Reproduced with permission from ref. 294. Copyright 2019, American Chemical Society.

nanocatalysts have been applied in effective biomass transformation.290-295 Li, Luque and co-workers applied hollow Fe-Co supported on carbon (FeCo/C) derived from bimetallic Fe/ Co-MIL-45b for chemical conversions of biomass-derived platform chemicals.²⁹⁰ In the aerobic oxidation of biomassderived 5-hydroxymethylfurfural (HMF) to 2,5-diformylfuran (DFF), FeCo/C(T) prepared by calcination at different temperatures ($T = 500, 600, 700 \text{ or } 800 \,^{\circ}\text{C}$) showed distinct activities. FeCo/C(500) exhibited the highest activity, with a complete conversion and >99% selectivity to DFF at 100 °C after 6 h (Fig. 19C). Jones and co-workers prepared Co/Cu-carbon (Co/ derived from Cu/Co MOF-74 furfural hydrogenation.292 The catalyst performance was investigated at 180 °C and a weight/volume flow rate (W/F) of 3.63 g_{cat} h mol⁻¹, and monometallic Co-C showed high conversion (50%) and high selectivity for 2-methylfuran (49%), while Cu-C had low conversion but high selectivity toward furfuryl alcohol. CoCu-C-400 (pyrolyzed at a temperature of 400 °C) with a partial Cu shell showed reactivities characteristic of Co-C. CoCu-C-600 with a full Cu shell had reactivities similar to those of Cu-C. Although bimetallic CoCu catalysts did not show activity/selectivity improvements compared to those of monometallic catalysts for furfural conversion, these results have demonstrated synthesis-structure-property correlations,

which would guide the future development of better catalysts. The conversion of lignin (10–35% by weight in biomass) to value-added chemicals, alternative fuels, and platform compounds is attractive. Bao, Ren and co-workers reported the use of bimetallic-MOF-derived Ni–Co/C materials with varying Ni/Co ratios as catalysts for lignin conversion into monophenols.²⁹⁴ In the hydrogenolysis of poplar lignin, Ni_{0.5}Co_{0.5}/C showed superior catalytic efficiency to Ni/C, with a yield of 55.2% to monophenols and a selectivity of 70.3% to guaiacol (Fig. 19D).

Chemical Science

5.1.2 Photocatalysis. Bimetallic MOF-derived porous nanomaterials have also been developed for photocatalysis, including photocatalytic degradation of organic pollutants, water splitting and CO_2 reduction.

Photocatalytic degradation of organic pollutants from wastewater is of ecological and environmental importance. Nanomaterials derived from bimetallic MOFs have shown high activity and stability in the degradation of organic pollutants, such as organic dyes and antibiotics. 266,279,296-299 Li and coworkers designed ZnO@C-N-Co core-shell nanocomposites derived from Zn/Co ZIF for the degradation of methyl orange (MO).297 When calcining Zn/Co ZIF at 600 °C, ZnO NPs generated from the ZIF-8 shell would aggregate and move to the hollow cavity while the internal Co NPs transferred inversely to the N-C shell, resulting in the unique ZnO@C-N-Co core-shell structure. Under the irradiation of a Xe lamp (300 W) for 2.5 h, ZnO@C-N-Co exhibited a high degradation percentage of MO (99.5%), much higher than that of ZIF-67-600 (29.4%) and ZIF-8-600 (41.9%). The superior performance of ZnO@C-N-Co could be attributed to the synergistic effect between the components, in which the porous carbon shell contributed to the stabilization of ZnO and the adsorption of reactants and Co NPs inhibited the recombination of electrons and holes (Fig. 20A).

Photocatalytic water splitting for hydrogen production is a promising route to convert solar energy into renewable hydrogen energy. 300,301 Bimetallic MOF-derived nanomaterials, such as Fe-Ni-P,302 CuS/ZnS,303 Co-doped Zn1-xCdxS,304 yolkshell CdS microcubes,305 and NiS/ZnxCd1-xS,306 have been applied in photocatalytic water splitting for hydrogen production. As an example, Shi, Cheng and co-workers constructed non-noble metal co-catalyst/solid solution heterojunction NiS/ $Zn_xCd_{1-x}S$ derived from Ni- Zn_xCd_{1-x} -MOF for the production of hydrogen (Fig. 20B).³⁰⁶ Under visible-light irradiation ($\lambda > 420$ nm), NiS/Zn_{0.5}Cd_{0.5}S exhibited a high HER rate of 16.78 mmol g⁻¹ h⁻¹, much higher than those of NiS/ZnS (0.09 mmol g⁻¹ h^{-1}), NiS/ZnS (0.09 mmol $g^{-1} h^{-1}$) and NiS/CdS (3.52 mmol g^{-1} h^{-1}). The tuning of the Zn/Cd ratio in heterojunction $Zn_xCd_{1-x}S$ pointed to an optimized x of 0.5 to achieve a good balance between the light absorption capacity of the catalyst and edge of the conduction band. The co-catalyst NiS could further accelerate the water dissociation kinetics to improve the photocatalytic hydrogen evolution activity. Furthermore, constructing composites of co-catalysts and bimetallic MOF-derived photocatalysts, such as Cu_{0.9}Co_{2.1}S₄@MoS₂,³⁰⁷ CdS/Zn_xCo_{3-x}O₄,³⁰⁸ Pt-ZnO-Co₃O₄,²⁶² Pt-ZnS-CoS,²⁶² Pt-Zn₃P₂-CoP,²⁶² and MoS₂@-ZnCoS,256 can greatly enhance the activity for photocatalytic hydrogen evolution.

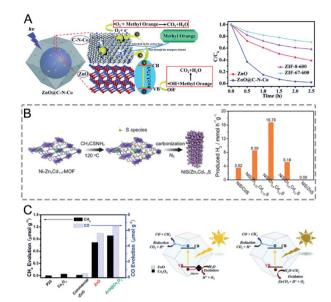


Fig. 20 (A) Proposed mechanism of the photodegradation of organic pollutants using the as-prepared core–shell ZnO@C–N–Co as the catalyst (left). Photodegradation curves of MO over various catalysts under irradiation with UV-vis light (right). Reproduced with permission from ref. 297. Copyright 2017, Royal Society of Chemistry. (B) Schematic illustration of the synthetic procedure for NiS/Zn_xCd_{1–x}S (left). Comparison of the photocatalytic HER rates of NiS/Zn_xCd_{1–x}S under visible-light irradiation (right). Reproduced with permission from ref. 306. Copyright 2018, Wiley-VCH. (C) Comparison of the photocatalytic activities of the photocatalysts under UV-vis irradiation, calculated according to how each compound evolved after 6 h. Schematic illustration of the photocatalytic CO₂ reduction with ZnO (middle) and ZnO@Co₃O₄ (right). Reproduced with permission from ref. 309. Copyright 2016, Royal Society of Chemistry.

Photocatalytic reduction of CO₂ is considered as an attractive approach to address fossil fuel shortage and carbon emission problems. Ye and co-workers prepared a ZnO@Co3O4 composite derived from ZIF-8@ZIF-67 for CO2 photoreduction to CH₄ and CO.³⁰⁹ Under UV-vis irradiation, ZnO@Co₃O₄ gave a CH₄ generation rate of 0.99 μ mol g⁻¹ h⁻¹, higher than those of ZnO derived from ZIF-8 and Co₃O₄ derived from ZIF-67 (Fig. 20C). In ZnO@Co₃O₄, ZnO played a main role in the catalytic transformation, while Co₃O₄ effectively protected ZnO from photocorrosion to enhance the photocatalytic stability. Deng, Peng and co-workers used carbonized cobalt composites (C-BMZIFs) derived from bimetallic Zn/Co-ZIF as co-catalysts for photocatalytic CO2 reduction.310 Under visible light irradiation with $[Ru(bpy)_3]^{2+}$ as the photosensitizer and triethanolamine (TEOA) as the electron donor, C-BMZIFs (Zn/Co = 3/1) delivered a high CO yield of 1.1×10^4 mmol g⁻¹ h⁻¹. Interestingly, decreasing the Zn/Co ratio in the Zn/Co-ZIF precursors could increase the size of Co particles in C-BMZIFs, which could favor the evolution of H2 against CO, resulting in the decrease of the CO/H₂ ratio in the produced syngas. Other nanomaterials derived from bimetallic MOFs, such as CuNi/C311 and ZnO/ NiO,312 have also been designed for photocatalytic reduction of CO_2 .

Perspective **Chemical Science**

5.1.3 Electrocatalysis. Functional nanomaterials derived from bimetallic MOFs have been employed as electrocatalysts for efficient and stable electrocatalysis of the ORR, OER, and HER, with applications in proton exchange membrane fuel cells (PEMFCs), alkaline fuel cells (AFCs), metal-air batteries and overall water splitting.313-315 Bimetallic MOF-derived nanomaterials have also been applied in electrochemical CO₂/N₂ reduction.

The ORR is the key reaction on the cathode of fuel cells and metal-air batteries. Bimetallic MOF derivatives,244 especially Fe and/or Co in N-doped carbon, 218,236,237,241,316 have been investigated for ORR electrocatalysis.317 These supported metal catalysts, in the form of atomically dispersed metal sites, metal

clusters, and metal NPs have demonstrated activities for the ORR. Deng and co-workers reported the controlled synthesis of NPs, atomic clusters (ACs), and SAs of Co catalysts on N-doped porous carbon derived from ZnCo-ZIFs for the ORR.318 Three samples with Zn/Co molar ratios of 0:1, 2:1, and 8:1 were synthesized, denoted as Co-ZIF, ZnCo-ZIF-2, and ZnCo-ZIF-8, respectively. Upon pyrolysis at 1173 K in Ar and subsequent reflux treatment in H₂SO₄ solution, Co-ZIF, ZnCo-ZIF-2, and ZnCo-ZIF-8 transformed into Co-NPs@NC, Co-ACs@NC, and Co-SAs@NC nanocomposites, respectively (Fig. 21A). These catalysts showed size-dependent ORR activity in a 0.1 M KOH electrolyte. Co-SAs@NC exhibited a superior activity with a halfwave potential $(E_{1/2})$ of 0.82 V, outperforming those of Co-

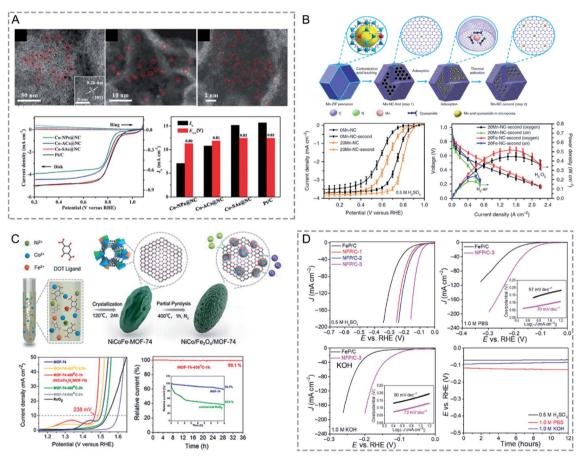


Fig. 21 (A) TEM images of Co-NPs@NC (left top), HAADF-STEM images of Co-ACs@NC (middle top) and Co-SAs@NC (right top). ORR polarization curves obtained using RRDEs at 1600 rpm and J_k at 0.6 V and $E_{1/2}$ for synthesized Co-NPs@NC, Co-ACs@NC, Co-SAs@NC and Pt/C catalysts (bottom). Reproduced with permission from ref. 318. Copyright 2019, Wiley-VCH. (B) Schematic of atomically dispersed MnN₄ site catalyst synthesis (top). Steady-state ORR polarization plots in 0.5 M H₂SO₄ electrolytes (Pt/C catalyst reference was studied in 0.1 M HClO₄) to study the effect of synthesis steps (that is, first doping and second adsorption) on Mn-N-C catalyst activity (left bottom). Fuel cell performance of the best-performing 20Mn-NC-second and 20Fe-NC-second catalysts under both H_2/O_2 and H_2/air conditions. Error bars represent the standard deviation from at least three independent measurements (right bottom). Reproduced with permission from ref. 239. Copyright 2018, Nature Publishing Group. (C) Scheme of the fabrication of trimetal NiCoFe-MOF-74 and the partial pyrolysis of NiCoFe-MOF-74 to NiCo/Fe $_3$ O $_4$ / MOF-74 (top). OER polarization curves of NiCoFe-MOF-74 and the derived partial pyrolyzed and completely pyrolyzed samples at 1600 rpm (left bottom). Relative current of initial current density at a constant potential of 1.47 V as a function of test time (chronoamperometric method) (right bottom). NiCoFe-MOF-74-400 °C-1 h (NiCo/Fe₃O₄/MOF-74) (red curve), MOF-74 (blue curve), and commercial RuO₂ (green curve). Reproduced with permission from ref. 265. Copyright 2018, American Chemical Society. (D) LSV curves of FeP/C and NFP/C-3 in 0.5 M H_2SO_4 and 1.0 M PBS and 1.0 M KOH solutions. Chronopotentiometry curves at a constant current density of 10 mA cm⁻² for 12 hours of NFP/C-3 in 0.5 M H₂SO₄, 1.0 M PBS, and 1.0 M KOH solutions. Reproduced with permission from ref. 228. Copyright 2019, American Association for the Advancement of Science.

Chemical Science Perspective

ACs@NC (0.81 V) and Co-NPs@NC (0.80 V). The determined electron transfer number of Co-SAs@NC is above 3.9, higher than those of Co-ACs@NC and Co-NPs@NC. These results demonstrated that isolated single Co atoms could provide maximum atom-utilization and be well stabilized by an Ndoped carbon support to show superior reactivity and stability. Besides Fe and Co, Mn-based catalysts are promising alternatives to address the insufficient durability of ORR catalysts. Wang, Wu and co-workers synthesized an atomically dispersed Mn-N-C catalyst for the ORR, obtained by calcination of MnZn-ZIF-8 followed by adsorption and thermal activation processes to increase the density of MnN₄ active sites (Fig. 21B).²³⁹ The 20Mn-NC-second catalyst (where 20 represents the molar percentage of Mn against the total metals for the synthesis of MnZn-ZIF-8; second refers to the second adsorption step) exhibited the most positive $E_{1/2}$ of 0.8 V. Mn-NC-first showed poor ORR activity due to insufficient density of active sites. The 20Mn-NC-second catalyst showed a H₂O₂ yield of less than 2%, indicating a four-electron reduction pathway. The 20Mn-NCsecond catalyst as a cathode in membrane electrode assemblies for fuel cells showed a power density of up to 0.46 W cm⁻².

Efficient OER electrocatalysis is important for various energyrelated processes, such as electrochemical water splitting and rechargeable metal-air batteries. Bimetallic MOF-derived metals/ alloys embedded in carbon,319 metal compounds248,261 and their carbon composites^{233,320-322} have demonstrated OER activity.^{323,324} Xu and co-workers applied FeCo-P/C nanocomposites derived from bimetallic MOFs for the OER.²³² Fe_rCo_v bimetallic MOFs with various Fe/Co ratios (x = 1, 2 and y = 1, 2) were employed as precursors to synthesize Fe_xCo_y-P/C. The overpotentials of Fe_x-Co_v-P/C in 1.0 M KOH at a current density of 10 mA cm⁻² showed a trend of Fe_1Co_1-P/C (360 mV) < Fe_1Co_2-P/C (362 mV) < Fe_2Co_1-P/C P/C (368 mV). All the Fe_xCo_y-P/C materials exhibited a better OER activity than their Fe_xCo_y/C without P-doping. The authors demonstrated that both P- and Fe-doping could reduce the resistance of charge transfer to accelerate the electron transfer and thus improve the OER activity. Considering that the complete decomposition of MOFs usually leads to a dramatic decrease of the surface area and pore structure, partial decomposition of bimetallic MOFs can preserve the porous structure to a certain extent for effective substrate diffusion while producing active metal NPs. Li and co-workers reported the synthesis of NiCo/Fe₃O₄/MOF-74 through controlled pyrolysis of trimetallic NiCoFe-MOF-74 for efficient OER electrocatalysis (Fig. 21C).²⁶⁵ The obtained NiCo/Fe₃O₄/MOF-74 retained 68% of the specific surface area of the pristine NiCoFe-MOF-74 (820 m² g⁻¹). In NiCo/Fe₃O₄/MOF-74, NiCo/Fe₃O₄ heterostructures with a NiCo alloy enriched in the core and Fe₃O₄ distributed on the shell were well dispersed in the partially retained MOF-74 structure. In a 1.0 M KOH electrolyte, NiCo/Fe₃O₄/MOF-74 exhibited an overpotential of 238 mV at 10 mA cm⁻² on a glassy carbon electrode, surpassing those of NiCoFe-MOF-74 (270 mV), the totally decomposed NiCoFe-MOF-74 derivative (366 mV) and the commercial RuO2 catalyst (310 mV). NiCo/Fe3O4/MOF-74 could retain 99.1% of its initial OER activity after 36 h. The excellent activity and stability of NiCoFe-MOF-74 for the OER could be attributed to the porous structures of MOF-74 and the synergistic effect between NiCo and ${\rm Fe_3O_4}$.

Efficient and inexpensive HER electrocatalysis to produce hydrogen from water splitting is of significant importance. Bimetallic MOF-derived materials, especially Mo-based materials³²⁵ and metal nitrides/phosphides/sulphides, ^{253,254,258,259,326} have been intensively investigated due to their favourable hydrogen adsorption energy toward the HER.327 Lou and coworkers synthesized carbon-supported Ni-doped FeP nanocrystals from Ni-doped MIL-88A as HER electrocatalysts.228 Nidoped MIL-88A was treated with phytic acid and subsequent pyrolysis under Ar and H2 to obtain Ni-doped FeP/C. The overpotential at 10 mA cm⁻² of NFP/C-3 (Ni/Fe atomic ratio of 3) was 72, 117, and 95 mV in 0.5 M H_2SO_4 (pH = 0), 1.0 M phosphatebuffered saline (pH \approx 7) and 1.0 M KOH (pH = 14), respectively (Fig. 21D). The NFP/C-3 electrocatalyst also exhibited good stability over the full pH range. The carbon support is important to structural integrity and catalytic performance. NFP-3 without carbon showed degradation of electrocatalytic activity and stability. XPS analysis and DFT calculations demonstrated that Ni doping could weaken the strong hydrogen adsorption on pure FeP to favour the HER.

Highly active and robust bimetallic MOF-derived multifunctional electrocatalysts for the ORR, OER and/or HER can be applied for efficient rechargeable metal-air batteries 185,219,224,315 and overall water splitting. 230,233,258,328-330 Very recently, Xu and co-workers synthesized a capsular carbon embedded with ironnickel phosphide NPs (FeNiP/NCH) through pyrolysis of capsular-MOF followed by phosphidation with melamine.94 FeNiP/NCH was employed as a trifunctional electrocatalyst for the ORR/OER/HER. In 1.0 M KOH solution, FeNiP/NCH obtained a current density of 10 mA cm⁻² at overpotentials of 250 and 216 mV for the OER and HER, respectively. For ORR electrocatalysis in 0.1 M KOH solution, FeNiP/NCH exhibited an $E_{1/2}$ of 0.75 V. When FeNiP/NCH was applied as both cathode and anode electrocatalysts for overall water splitting, a small cell voltage of 1.59 V was achieved at 10 mA cm⁻² (Fig. 22). When FeNiP/NCH was applied as the air electrode electrocatalyst in a Zn-air battery, a high power density (250 mW cm⁻²) could be achieved. In a galvanostatic discharge-charge cycling test at 5 mA cm⁻², the charge/discharge potentials were 1.89 and 1.23 V with a small voltage gap of 0.66 V. Moreover, no obvious voltage gap change was observed for 500 h, indicating the high stability of FeNiP/NCH.

Electrochemical CO₂ reduction is a potentially effective approach to produce synthetic fuels utilizing waste CO₂. Bimetallic MOF-derived nanomaterials demonstrated impressive FE for CO₂ reduction. Pan, Liu, Jiang and coworkers employed single-atom Ni implanted N doped carbon catalysts (Ni_{SA}-N_x-C) with a controlled N coordination number (x=2,3,4) derived from a MgNi-MOF-74 confined polypyrrole (PPy) composite for the electrochemical reduction of CO₂ to CO. The CO FE of Ni_{SA}-N_x-C followed a trend of Ni_{SA}-N₂-C > Ni_{SA}-N₃-C > Ni_{SA}-N₄-C. The TOF values for CO production of Ni_{SA}-N₂-C, Ni_{SA}-N₃-C and Ni_{SA}-N₄-C are 1622, 1120, and 225 h⁻¹ at -0.8 V, respectively. Ni_{SA}-N₂-C possessed the highest CO₂ reduction activity among the Ni_{SA}-N_x-C catalysts,

Perspective Chemical Science

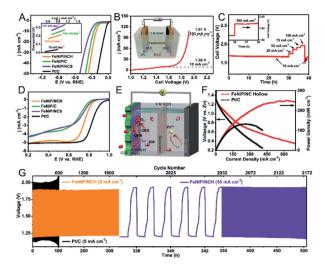


Fig. 22 (A) HER polarization of FeNiP/NCH and control samples in 1 M KOH at a scan rate of 10 mV s⁻¹. Inset: corresponding Tafel curves. (B) Polarization curve of the FeNiP/NCH ||FeNiP/NCH electrode in a twoelectrode configuration for water splitting. Inset: representation of the water-splitting device. (D) Catalytic stability at different current densities for around 40 h. Inset: the enlarged region of the curves for 100 mA cm⁻². Notably, in each increment of current density, the voltage could increase accordingly and then stabilize rapidly, whereafter, the cell voltage was also completely restored when the current density finally decreased to 10 mA cm⁻². (D) ORR polarization of FeNiP/NCH and control samples in O₂-saturated 0.1 M KOH solution with a RDE rotation rate of 1600 rpm. (E) Representation of a Zn-air battery (GDF: gas diffusion film). (F) Battery voltage and power density of Zn-air batteries. (G) Galvanostatic discharge-charge cycling curves of rechargeable Zn-air batteries with FeNiP/NCH and Pt/C catalysts on Ni foam, respectively. Reproduced with permission from ref. 94. Copyright 2019, American Chemical Society.

attributed to the favorable formation of the COOH* intermediate on low coordinated Ni–N₂ sites. Sun, Han and co-workers applied MOF-derived In-Cu bimetallic oxide catalysts (InCuO-x, where x is the Cu/In molar ratio) for CO₂ electroreduction.³³² InCuO-0.92 showed a highest FE of 92.1% at a potential of -0.8 V, which was 1.1, 1.3, 1.7, and 3.0 times higher than that of InCuO-0.72, InCuO-0.55, InCuO-0.37, and InCuO-0.15, respectively. The increase of x led to enhanced CO₂ reduction activity, indicating the synergistic effect between In oxides and Cu oxides to lead to stronger CO₂ adsorption, a higher electrochemical surface area and lower charge transfer resistance.

Electrochemical N_2 reduction (NNR) under ambient conditions is a promising sustainable route for ammonia synthesis.³³⁴ The related study on bimetallic MOF derivatives for NNR is still in its infancy. Recently, Qin, Cho and co-workers synthesized MoFe embedded in phosphorus-doped carbon microspheres (MoFe-PC) derived from bimetallic MoFe-MOFs for electrocatalytic NNR.³³⁵ The MoFe-PC catalyst gave a NH₃ formation rate of 34.23 μ g h⁻¹ mg_{cat.}⁻¹ with a high FE of 16.83% at -0.5 V, surpassing those of Mo–C (12.52 μ g h⁻¹ mg_{cat.}⁻¹, FE: 9.67%), Fe–C (17.83 μ g h⁻¹ mg_{cat.}⁻¹, FE: 7.69%), and MoFe–C (24.73 μ g h⁻¹ mg_{cat.}⁻¹, FE: 12.47%) prepared from pyrolysis of Mo-MOF, Fe-MOF, and MoFe-MOF without phosphorization, respectively. The superior performance of MoFe-PC for NNR can be

attributed to the synergistic effect of Mo and Fe oxides and P-doped carbon.

5.2 Energy storage and conversion


Bimetallic MOF-derived nanomaterials have attracted significant attention for energy storage applications such as supercapacitors and rechargeable batteries.^{336–339}

5.2.1 Supercapacitors. Bimetallic compounds (hydroxides, ^{250,251} oxides, ^{245,340,341} and sulphides ^{193,255}) and their carbon composites, ^{342–344} as well as metal@carbon composites ^{345–347} have been employed as electrode materials for supercapacitors.

to monometallic compounds, compounds can enable richer redox reactions and higher electrical conductivity owing to charge transfer between different ions. Bimetallic compounds with tuneable compositions reveal facile and reversible faradaic behaviors for excellent electrochemical capacitors. Bimetal oxides derived from bimetallic MOFs have high specific capacities but may suffer from unsatisfactory conductivity. Converting bimetallic MOFs into phosphides and sulphides can improve the electrical conductivity. For example, Xia and co-workers applied cobalt/nickel boride/ sulphide (Co-Ni-B-S) derived from bimetallic Co-Ni MOFs for supercapacitors.255 A Co-Ni MOF was first treated with sodium borohydride to lower the valence state of Co/Ni species (Co-Ni-B), followed by a sulfurization process to yield Co-Ni-B-S. When tested for supercapacitors, the Co-Ni-B-S electrode exhibited a high specific capacitance of 1281 F g^{-1} at 1 A g^{-1} , with a high retention of 92.1% after 10 000 cycles (Fig. 23A). The energy density of the Co-Ni-B-S electrode could reach as high as 50.0 Wh kg^{-1} at a power density of 857.7 W kg^{-1} , with a capacity retention of 87.7% at a 12 A g⁻¹ after 5000 cycles.

Metal compounds with complex structures can induce abundant hetero-interfaces and tune the electronic structure to facilitate ion/electron transfer and improve the specific capacity.245,252,348 Hu, Lou and co-workers fabricated CoO/Co-Cu-S hierarchical tubular heterostructures (HTHSs) for hybrid supercapacitors.348 CoO/Co-Cu-S was obtained by calcination of polyacrylonitrile (PAN)@MOF-74(Co/Cu) in air followed by annealing with S powder in a N₂ atmosphere. CoO/Co-Cu-S-2 (2 indicates the molar ratio of Co²⁺/Cu²⁺ in the precursors) delivered a specific capacity of 320 mA h g⁻¹ at a current density of 2.0 A g^{-1} , higher than that of CoO/Co-Cu-S-1 (192 $mA h g^{-1}$), CoO/Co-Cu-S-0.5 (167 $mA h g^{-1}$), CoO/Co-Cu-S-2nanoneedles without a tubular structure (135 mA h g^{-1}), monometallic CoO/CoS_x nanofibers (110 mA h g⁻¹) and $Cu_{1.81}S$ nanofibers (97 mA h g^{-1}). A hybrid supercapacitor constructed with CoO/Co-Cu-S-2 and activated carbon electrodes showed a high and stable energy density of 90.7 Wh kg^{-1} at a power density of 800 W kg^{-1} .

Constructing metal compound and carbon composites can improve the electrical conductivity, accommodate the volumetric change, and prevent the aggregation and dissolution of the metal compounds, thereby improving the rate capability and cycling stability. Cai, Zhang and co-workers synthesized bimetallic nickel cobalt sulphide embedded nitrogen-doped carbon composites (Ni-Co-S-n/NC, n represents the Ni/Co

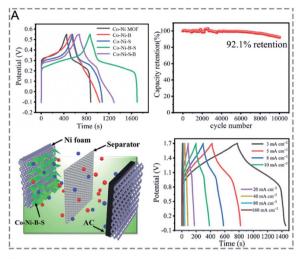

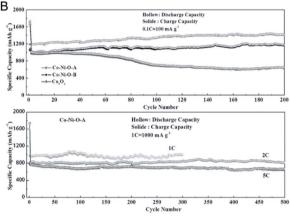


Fig. 23 (A) GCD plots of the prepared samples and cycling life of Co-Ni-B-S at 15 A $\rm g^{-1}$ (top). Schematic illustration of the asymmetric Co-Ni-B-S/NF//AC/NF device and GCD profiles at various current densities in the voltage range of 0 to 1.7 V (bottom). Reproduced with permission from ref. 255. Copyright 2019, Wiley-VCH. (B) Cycling performances of various products of Co-Ni-O-A, Co-Ni-O-B, and Co₃O₄ at 100 mA $\rm g^{-1}$ (0.1C) and high-rate cycling performances of Co-Ni-O-A. Reproduced with permission from ref. 243. Copyright 2015, Wiley-VCH.

molar ratio) with a hollow spherical structure for supercapacitors. 344 The Ni–Co–S-0.5/NC composite showed high specific capacities of 543.9 and 366.0C $\rm g^{-1}$ at 1 and 20 A $\rm g^{-1}$, respectively. An asymmetric supercapacitor based on the hollow Ni–Co–S-0.5/NC composite as the cathode exhibited good electrochemical performance with a high energy density of 39.6 W h kg $^{-1}$ at a power density of 808 W kg $^{-1}$.

5.2.2 Batteries. Materials derived from bimetallic MOFs have been investigated in a variety of batteries, including LIBs,³⁴⁹ sodium-ion batteries (SIBs),³⁵⁰ LOBs,³⁵¹ *etc*.

For LIBs, bimetallic oxides with complex chemical compositions have been designed to provide enhanced electrical conductivity and rich redox-active sites. ²⁴³,352-354 Sun, Wang and co-workers used Ni $_x$ Co $_{3-x}$ O $_4$ nanorods derived from Co/Ni-MOF-74 for lithium storage. ²⁴³ Co/Ni-MOF-74 A (Co: Ni = 9:1) and Co/Ni-MOF-74 B (Co: Ni = 2:1) afforded Ni $_{0.3}$ Co $_{2.7}$ O $_4$ and NiCo $_2$ O $_4$ after calcination at 450 °C in air, respectively.

Ni $_{0.3}$ Co $_{2.7}$ O $_4$ nanorods exhibited a large reversible Li-storage capacity of 1410 mA h g $^{-1}$ after 200 cycles at 100 mA g $^{-1}$, which was higher than that of NiCo $_2$ O $_4$ (1157 mA h g $^{-1}$) and Co $_3$ O $_4$ (625 mA h g $^{-1}$). Ni $_{0.3}$ Co $_{2.7}$ O $_4$ also showed large reversible capacities of 812 and 656 mA h g $^{-1}$ after 500 cycles at large current densities of 2 and 5 A g $^{-1}$, respectively (Fig. 23B). The excellent performances of Ni $_{0.3}$ Co $_{2.7}$ O $_4$ could be attributed to the mesoporous nanorod structure and the synergistic effect of two active metal oxides. Hybrid metal oxides with complex structures, such as ZnO/ZnFe $_2$ O $_4$ sub-microcubes, $_3^{355}$ Fe $_2$ O $_3$ @-NiCo $_2$ O $_4$ nanocages, $_4^{246}$ and CuO@NiO hollow spheres, $_4^{247}$ have been designed to accommodate large volume variation and shorten the lithium-ion diffusion length.

Embedding bimetal oxides in porous carbon can accommodate volume change and enhance electron/ion transport to greatly enhance the lithium storage performance. In this regard, bimetallic MOF-derived bimetallic oxide/carbon composites, such as $\text{CuCo}_2\text{O}_4/\text{C},^{356}$ $\text{ZnFe}_2\text{O}_4/\text{C}@\text{N-doped}$ carbon nanotubes, 357 and $\text{ZnO/ZnFe}_2\text{O}_4/\text{C},^{358}$ have been designed as anode materials for LIBs. In addition, other bimetal alloys and compounds (sulphides and phosphides) supported on carbon composites 234,235,344,345,359,360 derived from bimetallic MOFs were also reported as anode materials for LIBs.

MOF-derived bimetallic compounds and their carbon composites can also be applied as anodes for SIBs. Bimetallic MOF-derived metal compounds, such as CoFe₂O₄ (ref. 361) and Co₃O₄/ZnO,³⁶² could deliver high capacities but may suffer from poor rate capability and cycling stability due to a low electrical conductivity and large volume variation during charge/discharge processes. Bimetallic MOF-derived metal compound/carbon composites such as (Co_{0.5}Ni_{0.5})₉S₈/N-C²³¹ and Ti-doped-CoO@C,³⁶³ have been demonstrated as high-performance anode materials for SIBs. The porous carbon components can facilitate electron/ion transport and improve the structural integrity, and the metal compound components can deliver high capacities for sodium storage.

Bimetallic MOF-derived materials have also been applied as cathode materials for LOBs. Bimetallic MOF-derived metal compounds and their carbon composites, such as Co–Mn–O nanocubes, ³⁵² Co₃O₄@graphitic porous carbon, ³⁶⁴ and ZnO/ZnFe₂O₄/C nanocages, ³⁶⁵ have showed high performance in LOBs. In metal compound/carbon composites, the carbon supports with a large pore volume are beneficial for mass transportation and accommodation of discharge products (*e.g.*, LiO₂), and the well distributed catalysts accelerate oxygen-related redox reactions.

6. Conclusions and prospects

Bimetallic MOFs increase the complexity of MOF materials. Bimetallic MOFs can be divided into two categories according to the metal distribution, namely, solid solution and core-shell bimetallic MOFs. In solid solution bimetallic MOFs, two different metal ions have delocalized or even homogeneous distributions throughout the whole MOF crystals. Direct synthesis, post-synthetic modifications, and template synthesis have been applied for the preparation of solid solution

Perspective **Chemical Science**

bimetallic MOFs. A variety of techniques should be combined to well characterize the composition, location, and arrangement of metals in the synthesized bimetallic MOFs. Many studies lack detailed characterization to identify the metal arrangements within the frameworks, either mixed in the same SBUs or separated in different SBUs. The identification of the metal arrangements in bimetallic MOFs is of vital importance to correlate the metal mixing patterns with properties.

Two MOFs with different metal centres can be assembled into core-shell bimetallic MOFs. Seed-induced growth, postsynthetic exchange, and one-pot synthesis have been developed for the synthesis of core-shell bimetallic MOFs. The assembly of core-shell structures usually leads to distorted interfaces with defects and modified crystal structures and thus induces new mechanical, electronic, and catalytic properties. In future work, detailed characterization of the interfaces is expected, which will improve the fundamental understanding of the assembly process and establish structure-property relationships.

Bimetallic MOFs with complex compositions and structures frequently show superior properties to their monometallic counterparts. Metal substitution in the SBUs can tune the stability, flexibility, pore structure, and electronic structure of bimetallic MOFs. The possibility to tune the physical and chemical properties provides bimetallic MOFs with great promise in many applications, including gas adsorption, catalysis, energy storage and conversion, and luminescence sensing. Moreover, bimetallic MOFs with well-defined crystal structures are suitable for atomically precise structural characterization and computational modelling to achieve fundaunderstanding of the structure-performance relationship. Despite these advantages, the industrial applications of bimetallic MOFs are restricted due to their low stability, microporous structure, blockage of active sites, and poor conductivity.

Especially, the stability issue of bimetallic MOFs should be addressed if they are to be applied in industrial applications. Much effort has been devoted to improving the stability of MOFs, including direct synthesis of high-valent metalcarboxylate or low-valent metal-azolate MOFs and postsynthetic modification of organic linkers or coating of a protective layer. General and facile strategies are to be developed to be applicable to different bimetallic MOF systems. It is necessary to systematically investigate the chemical, thermal, and mechanical stability of bimetallic MOFs to guide the synthesis of very stable bimetallic MOFs for targeted applications.

Moreover, bimetallic MOFs can serve as excellent precursors/ templates for the synthesis of a variety of nanostructured materials, including carbon composites, metal compounds, and MOF composites. The achieved success in controlling the compositions and distributions of metal ions in bimetallic MOFs can allow the tuning of compositions and structures of the obtained metal atoms/NPs/compounds. The homogeneous doping of heteroatoms (N, P, S, etc.) in the organic linkers can be inherited to the derived carbon materials to stabilize the metal species and facilitate the activity. The different

coordination abilities of metal ions with the organic linkers in bimetallic MOFs offer the possibility to selectively transform part of the framework to metal NPs/compounds while preserving the rest of the framework to retain the porosity to

Bimetallic MOF derivatives show exposed active sites, good stability and conductivity, enabling them to extend their applications in the catalysis of more challenging reactions under harsh conditions and electrochemical energy storage and conversion. Despite the achieved success in the transformation of bimetallic MOFs to functional materials, several common drawbacks persist during the transformation process: (1) the poor control over the pore structure of bimetallic MOF-derived materials and (2) the inevitable aggregation of metal NPs/ compounds. To address these issues, template-assisted synthesis and controlled transformation to "quasi-MOFs" are currently emerging to boost the development of bimetallic MOF-derived nanomaterials. Template-assisted synthesis utilizing SiO2, etc., can provide robust skeletons to prevent the architecture from collapsing and serious aggregation of metal NPs/compounds during calcination. Besides, controlled transformation into quasi-MOFs can not only allow the exposure of active sites, but also preserve the porous structures to a certain extent. The unique features of quasi-MOFs remain to be explored, which will pave the way to the development of the next-generation of functional materials.

Although many challenges still exist, the rapid development of bimetallic MOFs and their derivatives in recent years will lead to a promising future. Continued research and development in this exciting area can be expected to enable the practical applications of bimetallic MOF-based materials.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors thank the editor for the kind invitation. We would like to thank the AIST and National Natural Science Foundation of China (NSFC-21875207) for financial support.

Notes and references

- 1 S. Kitagawa, R. Kitaura and S.-i. Noro, Angew. Chem., Int. Ed., 2004, 43, 2334-2375.
- 2 H. Furukawa, K. E. Cordova, M. O'Keeffe and O. M. Yaghi, Science, 2013, 341, 974-986.
- 3 H. Li, L. Li, R.-B. Lin, W. Zhou, Z. Zhang, S. Xiang and B. Chen, EnergyChem, 2019, 1, 100006.
- 4 M. Woellner, S. Hausdorf, N. Klein, P. Mueller, M. W. Smith and S. Kaskel, Adv. Mater., 2018, 30, 1704679.
- 5 X. Zhao, Y. Wang, D.-S. Li, X. Bu and P. Feng, Adv. Mater., 2018, 30, 1705189.
- 6 L. Chen and Q. Xu, *Matter*, 2019, 1, 57–89.
- 7 D. Li, H.-Q. Xu, L. Jiao and H.-L. Jiang, EnergyChem, 2019, 1, 100005.

8 C. Xu, R. Fang, R. Luque, L. Chen and Y. Li, *Coord. Chem. Rev.*, 2019, **388**, 268–292.

Chemical Science

- 9 W. Liu, W. P. Lustig and J. Li, EnergyChem, 2019, 1, 100008.
- 10 K. Lu, T. Aung, N. Guo, R. Weichselbaum and W. Lin, Adv. Mater., 2018, 30, 1707634.
- 11 T. Simon-Yarza, A. Mielcarek, P. Couvreur and C. Serre, *Adv. Mater.*, 2018, **30**, 1707365.
- 12 H. Wang, Q.-L. Zhu, R. Zou and Q. Xu, Chem, 2017, 2, 52-80.
- 13 Z. Liang, R. Zhao, T. Qiu, R. Zou and Q. Xu, *EnergyChem*, 2019, **1**, 100001.
- 14 X. Li, X. Yang, H. Xue, H. Pang and Q. Xu, *EnergyChem*, 2020, 2, 100027.
- 15 X. Yang and Q. Xu, Cryst. Growth Des., 2017, 17, 1450-1455.
- 16 A. D. Burrows, CrystEngComm, 2011, 13, 3623-3642.
- 17 M. Y. Masoomi, A. Morsali, A. Dhakshinamoorthy and H. Garcia, *Angew. Chem., Int. Ed.*, 2019, **58**, 15188–15205.
- 18 L. Feng, K.-Y. Wang, G. S. Day and H.-C. Zhou, *Chem. Soc. Rev.*, 2019, **48**, 4823–4853.
- 19 M. L. Foo, R. Matsuda and S. Kitagawa, *Chem. Mater.*, 2014, **26**, 310–322.
- 20 J. E. Mondloch, W. Bury, D. Fairen-Jimenez, S. Kwon, E. J. DeMarco, M. H. Weston, A. A. Sarjeant, S. T. Nguyen, P. C. Stair, R. Q. Snurr, O. K. Farha and J. T. Hupp, *J. Am. Chem. Soc.*, 2013, 135, 10294–10297.
- 21 P. Ji, Y. Song, T. Drake, S. S. Veroneau, Z. Lin, X. Pan and W. Lin, *J. Am. Chem. Soc.*, 2018, **140**, 433–440.
- 22 L. Chen, Z. Gao and Y. Li, Catal. Today, 2015, 245, 122-128.
- 23 L. Chen, S. Rangan, J. Li, H. Jiang and Y. Li, *Green Chem.*, 2014, **16**, 3978–3985.
- 24 S. Wu, L. Chen, B. Yin and Y. Li, Chem. Commun., 2015, 51, 9884–9887.
- 25 A. Aijaz, A. Karkamkar, Y. J. Choi, N. Tsumori, E. Rönnebro, T. Autrey, H. Shioyama and Q. Xu, *J. Am. Chem. Soc.*, 2012, 134, 13926–13929.
- 26 L. Chen, H. Chen, R. Luque and Y. Li, *Chem. Sci.*, 2014, 5, 3708–3714.
- 27 L. Chen, X. Chen, H. Liu and Y. Li, *Small*, 2015, **11**, 2642–2648.
- 28 L. Chen, R. Luque and Y. Li, *Chem. Soc. Rev.*, 2017, **46**, 4614–4630.
- 29 L. Chen, R. Luque and Y. Li, *Dalton Trans.*, 2018, 47, 3663–3668.
- 30 A. M. Rice, G. A. Leith, O. A. Ejegbavwo, E. A. Dolgopolova and N. B. Shustova, *ACS Energy Lett.*, 2019, 4, 1938–1946.
- 31 A. Dhakshinamoorthy, A. M. Asiri and H. Garcia, *Catal. Sci. Technol.*, 2016, 6, 5238–5261.
- 32 S. Abednatanzi, P. Gohari Derakhshandeh, H. Depauw, F.-X. Coudert, H. Vrielinck, P. Van Der Voort and K. Leus, *Chem. Soc. Rev.*, 2019, **48**, 2535–2565.
- 33 S. Dang, Q.-L. Zhu and Q. Xu, Nat. Rev. Mater., 2017, 3, 17075.
- 34 J.-K. Sun and Q. Xu, Energy Environ. Sci., 2014, 7, 2071-2100.
- 35 A. F. Sapnik, H. S. Geddes, E. M. Reynolds, H. H. M. Yeung and A. L. Goodwin, *Chem. Commun.*, 2018, **54**, 9651–9654.
- 36 M. Lammert, C. Glißmann and N. Stock, *Dalton Trans.*, 2017, **46**, 2425–2429.

- 37 M. Kim, J. F. Cahill, H. Fei, K. A. Prather and S. M. Cohen, J. Am. Chem. Soc., 2012, 134, 18082–18088.
- 38 H. Fei, J. F. Cahill, K. A. Prather and S. M. Cohen, *Inorg. Chem.*, 2013, **52**, 4011–4016.
- 39 M. A. Gotthardt, R. Schoch, S. Wolf, M. Bauer and W. Kleist, *Dalton Trans.*, 2015, 44, 2052–2056.
- 40 Q. Liu, H. Cong and H. Deng, *J. Am. Chem. Soc.*, 2016, **138**, 13822–13825.
- 41 K. A. Lomachenko, J. Jacobsen, A. L. Bugaev, C. Atzori, F. Bonino, S. Bordiga, N. Stock and C. Lamberti, J. Am. Chem. Soc., 2018, 140, 17379–17383.
- 42 C. Castillo-Blas, V. A. de la Peña-O'Shea, I. Puente-Orench, J. R. de Paz, R. Sáez-Puche, E. Gutiérrez-Puebla, F. Gándara and Á. Monge, Sci. Adv., 2017, 3, e1700773.
- 43 M. A. Syzgantseva, C. P. Ireland, F. M. Ebrahim, B. Smit and O. A. Syzgantseva, *J. Am. Chem. Soc.*, 2019, **141**, 6271–6278.
- 44 F. Trousselet, A. Archereau, A. Boutin and F.-X. Coudert, *J. Phys. Chem. C*, 2016, **120**, 24885–24894.
- 45 K. S. Park, Z. Ni, A. P. Côté, J. Y. Choi, R. Huang, F. J. Uribe-Romo, H. K. Chae, M. O'Keeffe and O. M. Yaghi, *Proc. Natl. Acad. Sci. U. S. A.*, 2006, **103**, 10186–10191.
- 46 M.-H. Zeng, B. Wang, X.-Y. Wang, W.-X. Zhang, X.-M. Chen and S. Gao, *Inorg. Chem.*, 2006, 45, 7069–7076.
- 47 Y. Wang, B. Bredenkötter, B. Rieger and D. Volkmer, *Dalton Trans.*, 2007, 689–696.
- 48 A. Nowacka, P. Briantais, C. Prestipino and F. X. Llabrés i Xamena, *Cryst. Growth Des.*, 2019, **19**, 4981–4989.
- 49 J. A. Botas, G. Calleja, M. Sánchez-Sánchez and M. G. Orcajo, *Langmuir*, 2010, 26, 5300–5303.
- 50 T. Wang, X. Li, W. Dai, Y. Fang and H. Huang, J. Mater. Chem. A, 2015, 3, 21044–21050.
- 51 J. A. Botas, G. Calleja, M. Sánchez-Sánchez and M. G. Orcajo, *Int. J. Hydrogen Energy*, 2011, 36, 10834–10844.
- 52 H. Yang, X.-W. He, F. Wang, Y. Kang and J. Zhang, *J. Mater. Chem.*, 2012, 22, 21849–21851.
- 53 A. Schejn, A. Aboulaich, L. Balan, V. Falk, J. Lalevée, G. Medjahdi, L. Aranda, K. Mozet and R. Schneider, *Catal. Sci. Technol.*, 2015, 5, 1829–1839.
- 54 Z. Zhou, L. Mei, C. Ma, F. Xu, J. Xiao, Q. Xia and Z. Li, *Chem. Eng. Sci.*, 2016, **147**, 109–117.
- 55 F. Nouar, T. Devic, H. Chevreau, N. Guillou, E. Gibson, G. Clet, M. Daturi, A. Vimont, J. M. Grenèche, M. I. Breeze, R. I. Walton, P. L. Llewellyn and C. Serre, *Chem. Commun.*, 2012, 48, 10237–10239.
- 56 F. Nouar, M. I. Breeze, B. C. Campo, A. Vimont, G. Clet, M. Daturi, T. Devic, R. I. Walton and C. Serre, *Chem. Commun.*, 2015, 51, 14458–14461.
- 57 L. J. Wang, H. Deng, H. Furukawa, F. Gándara, K. E. Cordova, D. Peri and O. M. Yaghi, *Inorg. Chem.*, 2014, 53, 5881–5883.
- 58 S.-T. Zheng, T. Wu, C. Chou, A. Fuhr, P. Feng and X. Bu, *J. Am. Chem. Soc.*, 2012, **134**, 4517–4520.
- 59 D. Feng, K. Wang, Z. Wei, Y.-P. Chen, C. M. Simon, R. K. Arvapally, R. L. Martin, M. Bosch, T.-F. Liu, S. Fordham, D. Yuan, M. A. Omary, M. Haranczyk, B. Smit and H.-C. Zhou, *Nat. Commun.*, 2014, 5, 5723.

60 S. Wongsakulphasatch, F. Nouar, J. Rodriguez, L. Scott, C. Le Guillouzer, T. Devic, P. Horcajada, J. M. Grenèche, P. L. Llewellyn, A. Vimont, G. Clet, M. Daturi and C. Serre, Chem. Commun., 2015, 51, 10194–10197.

Perspective

- 61 D. Kim, K. S. Song, O. Buyukcakir, T. Yildirim and A. Coskun, *Chem. Commun.*, 2018, 54, 12218–12221.
- 62 M. Dincă and J. R. Long, J. Am. Chem. Soc., 2007, 129, 11172-11176.
- 63 T. K. Prasad, D. H. Hong and M. P. Suh, *Chem. Eur. J.*, 2010, **16**, 14043–14050.
- 64 Q. Yao, J. Sun, K. Li, J. Su, M. V. Peskov and X. Zou, *Dalton Trans.*, 2012, 41, 3953–3955.
- 65 S. R. Caskey and A. J. Matzger, *Inorg. Chem.*, 2008, 47, 7942–7944.
- 66 M. Lalonde, W. Bury, O. Karagiaridi, Z. Brown, J. T. Hupp and O. K. Farha, *J. Mater. Chem. A*, 2013, **1**, 5453–5468.
- 67 C. K. Brozek and M. Dincă, Chem. Soc. Rev., 2014, 43, 5456–5467.
- 68 P. Deria, J. E. Mondloch, O. Karagiaridi, W. Bury, J. T. Hupp and O. K. Farha, *Chem. Soc. Rev.*, 2014, 43, 5896–5912.
- 69 C. K. Brozek and M. Dincă, J. Am. Chem. Soc., 2013, 135, 12886–12891.
- 70 J.-H. Liao, W.-T. Chen, C.-S. Tsai and C.-C. Wang, CrystEngComm, 2013, 15, 3377–3384.
- 71 Z. Wei, W. Lu, H.-L. Jiang and H.-C. Zhou, *Inorg. Chem.*, 2013, 52, 1164–1166.
- 72 C. K. Brozek, V. K. Michaelis, T.-C. Ong, L. Bellarosa, N. López, R. G. Griffin and M. Dincă, ACS Cent. Sci., 2015, 1, 252–260.
- 73 L. Mi, H. Hou, Z. Song, H. Han, H. Xu, Y. Fan and S.-W. Ng, *Cryst. Growth Des.*, 2007, 7, 2553–2561.
- 74 C. K. Brozek, A. F. Cozzolino, S. J. Teat, Y.-S. Chen and M. Dincă, *Chem. Mater.*, 2013, 25, 2998–3002.
- 75 S. Das, H. Kim and K. Kim, J. Am. Chem. Soc., 2009, 131, 3814-3815.
- 76 Z. Zhang, L. Zhang, L. Wojtas, P. Nugent, M. Eddaoudi and M. J. Zaworotko, *J. Am. Chem. Soc.*, 2012, **134**, 924–927.
- 77 L. Mi, H. Hou, Z. Song, H. Han and Y. Fan, *Chem. Eur. J.*, 2008, **14**, 1814–1821.
- 78 X. Song, T. K. Kim, H. Kim, D. Kim, S. Jeong, H. R. Moon and M. S. Lah, *Chem. Mater.*, 2012, 24, 3065–3073.
- 79 X.-S. Wang, M. Chrzanowski, L. Wojtas, Y.-S. Chen and S. Ma, *Chem. – Eur. J.*, 2013, **19**, 3297–3301.
- 80 C. Hon Lau, R. Babarao and M. R. Hill, *Chem. Commun.*, 2013, 49, 3634–3636.
- 81 P. Á. Szilágyi, P. Serra-Crespo, I. Dugulan, J. Gascon, H. Geerlings and B. Dam, *CrystEngComm*, 2013, 15, 10175–10178.
- 82 J. G. Santaclara, A. I. Olivos-Suarez, A. Gonzalez-Nelson, D. Osadchii, M. A. Nasalevich, M. A. van der Veen, F. Kapteijn, A. M. Sheveleva, S. L. Veber, M. V. Fedin, A. T. Murray, C. H. Hendon, A. Walsh and J. Gascon, *Chem. Mater.*, 2017, 29, 8963–8967.
- 83 M. S. Denny, L. R. Parent, J. P. Patterson, S. K. Meena, H. Pham, P. Abellan, Q. M. Ramasse, F. Paesani, N. C. Gianneschi and S. M. Cohen, *J. Am. Chem. Soc.*, 2018, **140**, 1348–1357.

- 84 R. Li, X. Ren, H. Ma, X. Feng, Z. Lin, X. Li, C. Hu and B. Wang, *J. Mater. Chem. A*, 2014, 2, 5724–5729.
- 85 T. Panda, S. Horike, K. Hagi, N. Ogiwara, K. Kadota, T. Itakura, M. Tsujimoto and S. Kitagawa, *Angew. Chem., Int. Ed.*, 2017, **56**, 2413–2417.
- 86 J.-S. M. Lee, Y.-i. Fujiwara, S. Kitagawa and S. Horike, *Chem. Mater.*, 2019, 31, 4205–4212.
- 87 D. Kim and A. Coskun, *Angew. Chem., Int. Ed.*, 2017, **56**, 5071–5076.
- 88 D. Liu, J. Wan, G. Pang and Z. Tang, *Adv. Mater.*, 2019, 31, 1803291.
- 89 H. J. Lee, W. Cho and M. Oh, *Chem. Commun.*, 2012, 48, 221–223.
- 90 K. Shen, L. Zhang, X. Chen, L. Liu, D. Zhang, Y. Han, J. Chen, J. Long, R. Luque, Y. Li and B. Chen, *Science*, 2018, 359, 206-210.
- 91 M. Qiao, Y. Wang, Q. Wang, G. Hu, X. Mamat, S. Zhang and S. Wang, *Angew. Chem., Int. Ed.*, 2020, **59**, 2688–2694.
- 92 J. Teng, M. Chen, Y. Xie, D. Wang, J.-J. Jiang, G. Li, H.-P. Wang, Y. Fan, Z.-W. Wei and C.-Y. Su, *Chem. Mater.*, 2018, **30**, 6458–6468.
- 93 Z. Zhang, Y. Chen, S. He, J. Zhang, X. Xu, Y. Yang, F. Nosheen, F. Saleem, W. He and X. Wang, *Angew. Chem., Int. Ed.*, 2014, 53, 12517–12521.
- 94 Y.-S. Wei, M. Zhang, M. Kitta, Z. Liu, S. Horike and Q. Xu, *J. Am. Chem. Soc.*, 2019, **141**, 7906–7916.
- 95 Z. Zhang, Y. Chen, X. Xu, J. Zhang, G. Xiang, W. He and X. Wang, *Angew. Chem., Int. Ed.*, 2014, 53, 429–433.
- 96 L. Chen, B. Huang, X. Qiu, X. Wang, R. Luque and Y. Li, *Chem. Sci.*, 2016, 7, 228–233.
- 97 L. Chen, W. Huang, X. Wang, Z. Chen, X. Yang, R. Luque and Y. Li, *Chem. Commun.*, 2017, 53, 1184–1187.
- 98 S. Furukawa, K. Hirai, K. Nakagawa, Y. Takashima, R. Matsuda, T. Tsuruoka, M. Kondo, R. Haruki, D. Tanaka, H. Sakamoto, S. Shimomura, O. Sakata and S. Kitagawa, *Angew. Chem., Int. Ed.*, 2009, 48, 1766–1770.
- 99 J. Tang, R. R. Salunkhe, J. Liu, N. L. Torad, M. Imura, S. Furukawa and Y. Yamauchi, *J. Am. Chem. Soc.*, 2015, 137, 1572–1580.
- 100 M. Zhao, K. Yuan, Y. Wang, G. Li, J. Guo, L. Gu, W. Hu, H. Zhao and Z. Tang, *Nature*, 2016, 539, 76–80.
- 101 T.-Y. Luo, C. Liu, X. Y. Gan, P. F. Muldoon, N. A. Diemler, J. E. Millstone and N. L. Rosi, J. Am. Chem. Soc., 2019, 141, 2161–2168.
- 102 H. J. Lee, Y. J. Cho, W. Cho and M. Oh, ACS Nano, 2013, 7, 491–499.
- 103 J. Zhuang, L.-Y. Chou, B. T. Sneed, Y. Cao, P. Hu, L. Feng and C.-K. Tsung, *Small*, 2015, **11**, 5551–5555.
- 104 F. Wang, S. He, H. Wang, S. Zhang, C. Wu, H. Huang, Y. Pang, C.-K. Tsung and T. Li, *Chem. Sci.*, 2019, **10**, 7755– 7761.
- 105 F. Wang, H. Wang and T. Li, *Nanoscale*, 2019, **11**, 2121–2125.
- 106 Y. Gu, Y.-n. Wu, L. Li, W. Chen, F. Li and S. Kitagawa, *Angew. Chem., Int. Ed.*, 2017, **56**, 15658–15662.
- 107 L. Feng, S. Yuan, J.-L. Li, K.-Y. Wang, G. S. Day, P. Zhang, Y. Wang and H.-C. Zhou, ACS Cent. Sci., 2018, 4, 1719–1726.

108 X. Song, S. Jeong, D. Kim and M. S. Lah, *CrystEngComm*, 2012, 14, 5753–5756.

Chemical Science

- 109 L. Chen, H. Chen and Y. Li, *Chem. Commun.*, 2014, **50**, 14752–14755.
- 110 L. Chen, X. Chen, H. Liu, C. Bai and Y. Li, *J. Mater. Chem. A*, 2015, 3, 15259–15264.
- 111 H. Liu, L. Chang, C. Bai, L. Chen, R. Luque and Y. Li, *Angew. Chem., Int. Ed.*, 2016, 55, 5019–5023.
- 112 W. Guo, W. Xia, K. Cai, Y. Wu, B. Qiu, Z. Liang, C. Qu and R. Zou, *Small*, 2017, **13**, 1702049.
- 113 H. Depauw, I. Nevjestić, J. De Winne, G. Wang, K. Haustraete, K. Leus, A. Verberckmoes, C. Detavernier, F. Callens, E. De Canck, H. Vrielinck and P. Van Der Voort, Chem. Commun., 2017, 53, 8478–8481.
- 114 T. Fukushima, S. Horike, H. Kobayashi, M. Tsujimoto, S. Isoda, M. L. Foo, Y. Kubota, M. Takata and S. Kitagawa, *J. Am. Chem. Soc.*, 2012, **134**, 13341–13347.
- 115 H. Li, W. Shi, K. Zhao, H. Li, Y. Bing and P. Cheng, *Inorg. Chem.*, 2012, 51, 9200–9207.
- 116 X. Song, M. Oh and M. S. Lah, *Inorg. Chem.*, 2013, 52, 10869–10876.
- 117 J. Yang, X. Wang, F. Dai, L. Zhang, R. Wang and D. Sun, *Inorg. Chem.*, 2014, 53, 10649–10653.
- 118 Y. Jiao, C. R. Morelock, N. C. Burtch, W. P. Mounfield, J. T. Hungerford and K. S. Walton, *Ind. Eng. Chem. Res.*, 2015, 54, 12408–12414.
- 119 J.-P. Zhang, H.-L. Zhou, D.-D. Zhou, P.-Q. Liao and X.-M. Chen, *Natl. Sci. Rev.*, 2017, 5, 907–919.
- 120 J. H. Choi, Y. J. Choi, J. W. Lee, W. H. Shin and J. K. Kang, *Phys. Chem. Chem. Phys.*, 2009, **11**, 628–631.
- 121 L. Sun, M. G. Campbell and M. Dincă, *Angew. Chem., Int. Ed.*, 2016, 55, 3566-3579.
- 122 E. A. Dolgopolova, A. J. Brandt, O. A. Ejegbavwo, A. S. Duke, T. D. Maddumapatabandi, R. P. Galhenage, B. W. Larson, O. G. Reid, S. C. Ammal, A. Heyden, M. Chandrashekhar, V. Stavila, D. A. Chen and N. B. Shustova, *J. Am. Chem. Soc.*, 2017, 139, 5201–5209.
- 123 G. Kaur, R. K. Rai, D. Tyagi, X. Yao, P.-Z. Li, X.-C. Yang, Y. Zhao, Q. Xu and S. K. Singh, *J. Mater. Chem. A*, 2016, 4, 14932–14938.
- 124 D.-D. Zhou, X.-W. Zhang, Z.-W. Mo, Y.-Z. Xu, X.-Y. Tian, Y. Li, X.-M. Chen and J.-P. Zhang, *EnergyChem*, 2019, 1, 100016.
- 125 P.-P. Cui, X.-D. Zhang, P. Wang, Y. Zhao, M. Azam, S. I. Al-Resayes and W.-Y. Sun, *Inorg. Chem.*, 2017, **56**, 14157– 14163.
- 126 Q.-G. Zhai, X. Bu, C. Mao, X. Zhao and P. Feng, *J. Am. Chem. Soc.*, 2016, **138**, 2524–2527.
- 127 R.-Q. Zou, H. Sakurai, S. Han, R.-Q. Zhong and Q. Xu, *J. Am. Chem. Soc.*, 2007, **129**, 8402–8403.
- 128 V. Bernales, M. A. Ortuño, D. G. Truhlar, C. J. Cramer and L. Gagliardi, *ACS Cent. Sci.*, 2018, 4, 5–19.
- 129 D. J. Xiao, E. D. Bloch, J. A. Mason, W. L. Queen, M. R. Hudson, N. Planas, J. Borycz, A. L. Dzubak, P. Verma, K. Lee, F. Bonino, V. Crocellà, J. Yano, S. Bordiga, D. G. Truhlar, L. Gagliardi, C. M. Brown and J. R. Long, *Nat. Chem.*, 2014, 6, 590–595.

- 130 P. Verma, K. D. Vogiatzis, N. Planas, J. Borycz, D. J. Xiao, J. R. Long, L. Gagliardi and D. G. Truhlar, *J. Am. Chem. Soc.*, 2015, **137**, 5770–5781.
- 131 D. Sun, F. Sun, X. Deng and Z. Li, *Inorg. Chem.*, 2015, 54, 8639–8643.
- 132 A. Nowacka, P. Briantais, C. Prestipino and F. X. Llabrés i Xamena, *ACS Sustainable Chem. Eng.*, 2019, 7, 7708–7715.
- 133 A. W. Stubbs, L. Braglia, E. Borfecchia, R. J. Meyer, Y. Román- Leshkov, C. Lamberti and M. Dincă, ACS Catal., 2018, 8, 596-601.
- 134 Á. Szécsényi, G. Li, J. Gascon and E. A. Pidko, *Chem. Sci.*, 2018, **9**, 6765–6773.
- 135 D. Y. Osadchii, A. I. Olivos-Suarez, Á. Szécsényi, G. Li, M. A. Nasalevich, I. A. Dugulan, P. S. Crespo, E. J. M. Hensen, S. L. Veber, M. V. Fedin, G. Sankar, E. A. Pidko and J. Gascon, ACS Catal., 2018, 8, 5542–5548.
- 136 D. M. Shakya, O. A. Ejegbavwo, T. Rajeshkumar, S. D. Senanayake, A. J. Brandt, S. Farzandh, N. Acharya, A. M. Ebrahim, A. I. Frenkel, N. Rui, G. L. Tate, J. R. Monnier, K. D. Vogiatzis, N. B. Shustova and D. A. Chen, Angew. Chem., Int. Ed., 2019, 58, 16533–16537.
- 137 H. G. T. Nguyen, L. Mao, A. W. Peters, C. O. Audu, Z. J. Brown, O. K. Farha, J. T. Hupp and S. T. Nguyen, *Catal. Sci. Technol.*, 2015, 5, 4444–4451.
- 138 C. Huang, R. Liu, W. Yang, Y. Li, J. Huang and H. Zhu, *Inorg. Chem. Front.*, 2018, 5, 1923–1932.
- 139 Y. Fu, L. Xu, H. Shen, H. Yang, F. Zhang, W. Zhu and M. Fan, *Chem. Eng. J.*, 2016, **299**, 135–141.
- 140 L. Mitchell, P. Williamson, B. Ehrlichová, A. E. Anderson, V. R. Seymour, S. E. Ashbrook, N. Acerbi, L. M. Daniels, R. I. Walton, M. L. Clarke and P. A. Wright, *Chem. – Eur. J.*, 2014, 20, 17185–17197.
- 141 J. M. Moreno, A. Velty, U. Díaz and A. Corma, *Chem. Sci.*, 2019, **10**, 2053–2066.
- 142 B. Iqbal, M. Saleem, S. N. Arshad, J. Rashid, N. Hussain and M. Zaheer, *Chem. Eur. J.*, 2019, 25, 10490–10498.
- 143 S. Smolders, J. Jacobsen, N. Stock and D. De Vos, *Catal. Sci. Technol.*, 2020, **10**, 337–341.
- 144 M. Giménez-Marqués, A. Santiago-Portillo, S. Navalón, M. Álvaro, V. Briois, F. Nouar, H. Garcia and C. Serre, J. Mater. Chem. A, 2019, 7, 20285–20292.
- 145 M. N. Timofeeva, V. N. Panchenko, N. A. Khan, Z. Hasan, I. P. Prosvirin, S. V. Tsybulya and S. H. Jhung, *Appl. Catal.*, *A*, 2017, **529**, 167–174.
- 146 F.-N. Shi, A. R. Silva, T.-H. Yang and J. Rocha, *CrystEngComm*, 2013, **15**, 3776–3779.
- 147 R. R. Kuruppathparambil, R. Babu, H. M. Jeong, G.-Y. Hwang, G. S. Jeong, M.-I. Kim, D.-W. Kim and D.-W. Park, *Green Chem.*, 2016, **18**, 6349–6356.
- 148 C. P. Krap, R. Newby, A. Dhakshinamoorthy, H. García, I. Cebula, T. L. Easun, M. Savage, J. E. Eyley, S. Gao, A. J. Blake, W. Lewis, P. H. Beton, M. R. Warren, D. R. Allan, M. D. Frogley, C. C. Tang, G. Cinque, S. Yang and M. Schröder, *Inorg. Chem.*, 2016, 55, 1076–1088.
- 149 L. M. Aguirre-Díaz, F. Gándara, M. Iglesias, N. Snejko, E. Gutiérrez-Puebla and M. Á. Monge, J. Am. Chem. Soc., 2015, 137, 6132–6135.

150 D. Saha, D. K. Hazra, T. Maity and S. Koner, *Inorg. Chem.*, 2016, 55, 5729–5731.

Perspective

- 151 A. M. Rasero-Almansa, M. Iglesias and F. Sánchez, *RSC Adv.*, 2016, **6**, 106790–106797.
- 152 Y. Hu, J. Zhang, H. Huo, Z. Wang, X. Xu, Y. Yang, K. Lin and R. Fan, *Catal. Sci. Technol.*, 2020, **10**, 315–322.
- 153 J. Castells-Gil, N. M. Padial, N. Almora-Barrios, J. Albero, A. R. Ruiz-Salvador, J. González-Platas, H. García and C. Martí-Gastaldo, *Angew. Chem., Int. Ed.*, 2018, 57, 8453–8457.
- 154 J. Tu, X. Zeng, F. Xu, X. Wu, Y. Tian, X. Hou and Z. Long, *Chem. Commun.*, 2017, 53, 3361–3364.
- 155 R. Navarro Amador, M. Carboni and D. Meyer, *RSC Adv.*, 2017, 7, 195–200.
- 156 Y. Lee, S. Kim, J. K. Kang and S. M. Cohen, *Chem. Commun.*, 2015, **51**, 5735–5738.
- 157 D. Sun, W. Liu, M. Qiu, Y. Zhang and Z. Li, *Chem. Commun.*, 2015, **51**, 2056–2059.
- 158 L. Zou, D. Feng, T.-F. Liu, Y.-P. Chen, S. Yuan, K. Wang, X. Wang, S. Fordham and H.-C. Zhou, *Chem. Sci.*, 2016, 7, 1063–1069.
- 159 C. Guo, J. Guo, Y. Zhang, D. Wang, L. Zhang, Y. Guo, W. Ma and J. Wang, *CrystEngComm*, 2018, **20**, 7659–7665.
- 160 H. Yoon, S. Lee, S. Oh, H. Park, S. Choi and M. Oh, *Small*, 2019, **15**, 1805232.
- 161 F. Zheng, D. Xiang, P. Li, Z. Zhang, C. Du, Z. Zhuang, X. Li and W. Chen, *ACS Sustainable Chem. Eng.*, 2019, 7, 9743–9749.
- 162 Q. Wang, C. Wei, D. Li, W. Guo, D. Zhong and Q. Zhao, *Microporous Mesoporous Mater.*, 2019, **286**, 92–97.
- 163 X.-L. Wang, L.-Z. Dong, M. Qiao, Y.-J. Tang, J. Liu, Y. Li, S.-L. Li, J.-X. Su and Y.-Q. Lan, *Angew. Chem., Int. Ed.*, 2018, 57, 9660–9664.
- 164 J. Li, W. Huang, M. Wang, S. Xi, J. Meng, K. Zhao, J. Jin, W. Xu, Z. Wang, X. Liu, Q. Chen, L. Xu, X. Liao, Y. Jiang, K. A. Owusu, B. Jiang, C. Chen, D. Fan, L. Zhou and L. Mai, ACS Energy Lett., 2019, 4, 285–292.
- 165 W. Zhou, D.-D. Huang, Y.-P. Wu, J. Zhao, T. Wu, J. Zhang, D.-S. Li, C. Sun, P. Feng and X. Bu, *Angew. Chem., Int. Ed.*, 2019, 58, 4227–4231.
- 166 F.-L. Li, Q. Shao, X. Huang and J.-P. Lang, *Angew. Chem., Int. Ed.*, 2018, 57, 1888–1892.
- 167 J. Duan, S. Chen and C. Zhao, Nat. Commun., 2017, 8, 15341.
- 168 H.-W. Lin, D. Senthil Raja, X.-F. Chuah, C.-T. Hsieh, Y.-A. Chen and S.-Y. Lu, *Appl. Catal.*, *B*, 2019, **258**, 118023.
- 169 J. Albo, M. Perfecto-Irigaray, G. Beobide and A. Irabien, *J. CO2 Util.*, 2019, 33, 157–165.
- 170 R. Wang, F. Kapteijn and J. Gascon, *Chem.-Asian J.*, 2019, **14**, 3452–3461.
- 171 A. Mahmood, W. Guo, H. Tabassum and R. Zou, *Adv. Energy Mater.*, 2016, **6**, 1600423.
- 172 Z. Zhao, J. Ding, R. Zhu and H. Pang, *J. Mater. Chem. A*, 2019, 7, 15519–15540.
- 173 K. Rui, G. Zhao, Y. Chen, Y. Lin, Q. Zhou, J. Chen, J. Zhu, W. Sun, W. Huang and S. X. Dou, *Adv. Funct. Mater.*, 2018, 28, 1801554.

- 174 S. Zhao, Y. Wang, J. Dong, C.-T. He, H. Yin, P. An, K. Zhao, X. Zhang, C. Gao, L. Zhang, J. Lv, J. Wang, J. Zhang, A. M. Khattak, N. A. Khan, Z. Wei, J. Zhang, S. Liu, H. Zhao and Z. Tang, *Nat. Energy*, 2016, 1, 16184.
- 175 M. Zhao, Y. Wang, Q. Ma, Y. Huang, X. Zhang, J. Ping, Z. Zhang, Q. Lu, Y. Yu, H. Xu, Y. Zhao and H. Zhang, *Adv. Mater.*, 2015, 27, 7372–7378.
- 176 L. Wang, Y. Wu, R. Cao, L. Ren, M. Chen, X. Feng, J. Zhou and B. Wang, ACS Appl. Mater. Interfaces, 2016, 8, 16736–16743.
- 177 G. Hai, X. Jia, K. Zhang, X. Liu, Z. Wu and G. Wang, *Nano Energy*, 2018, **44**, 345–352.
- 178 Q.-L. Zhu and Q. Xu, Chem. Soc. Rev., 2014, 43, 5468-5512.
- 179 X. Li, D.-D. Ma, C. Cao, R. Zou, Q. Xu, X.-T. Wu and Q.-L. Zhu, *Small*, 2019, **15**, 1902218.
- 180 F. Sun, G. Wang, Y. Ding, C. Wang, B. Yuan and Y. Lin, Adv. Energy Mater., 2018, 8, 1800584.
- 181 D. Senthil Raja, X.-F. Chuah and S.-Y. Lu, Adv. Energy Mater., 2018, 8, 1801065.
- 182 R. Zhao, Z. Liang, R. Zou and Q. Xu, *Joule*, 2018, 2, 2235–2259.
- 183 Y. Zhang, J. Liu, S.-L. Li, Z.-M. Su and Y.-Q. Lan, *EnergyChem*, 2019, **1**, 100021.
- 184 K.-B. Wang, Q. Xun and Q. Zhang, EnergyChem, 2020, 2, 100025.
- 185 B. Zhu, Z. Liang, D. Xia and R. Zou, *Energy Storage Mater.*, 2019, **23**, 757–771.
- 186 G. Xu, P. Nie, H. Dou, B. Ding, L. Li and X. Zhang, *Mater. Today*, 2017, 20, 191–209.
- 187 R. Díaz, M. G. Orcajo, J. A. Botas, G. Calleja and J. Palma, Mater. Lett., 2012, 68, 126–128.
- 188 J. Yang, C. Zheng, P. Xiong, Y. Li and M. Wei, *J. Mater. Chem. A*, 2014, **2**, 19005–19010.
- 189 H. Gholipour-Ranjbar, M. Soleimani and H. R. Naderi, *New J. Chem.*, 2016, **40**, 9187–9193.
- 190 Y. Jiao, J. Pei, D. Chen, C. Yan, Y. Hu, Q. Zhang and G. Chen, *J. Mater. Chem. A*, 2017, 5, 1094–1102.
- 191 L. Z. Shaofei Zhao, G. Cheng, L. Yu and H. Zeng, *Chin. Chem. Lett.*, 2019, **30**, 605–609.
- 192 D. Tian, N. Song, M. Zhong, X. Lu and C. Wang, *ACS Appl. Mater. Interfaces*, 2020, **12**, 1280–1291.
- 193 C. Chen, M.-K. Wu, K. Tao, J.-J. Zhou, Y.-L. Li, X. Han and L. Han, *Dalton Trans.*, 2018, 47, 5639–5645.
- 194 P. Nie, L. Shen, H. Luo, B. Ding, G. Xu, J. Wang and X. Zhang, *J. Mater. Chem. A*, 2014, 2, 5852–5857.
- 195 K. Saravanan, M. Nagarathinam, P. Balaya and J. J. Vittal, J. Mater. Chem., 2010, 20, 8329–8335.
- 196 P. Xiong, G. Zeng, L. Zeng and M. Wei, *Dalton Trans.*, 2015, 44, 16746–16751.
- 197 Y. s. Nanba, D. Asakura, M. Okubo, Y. Mizuno, T. Kudo, H. Zhou, K. Amemiya, J. Guo and K. Okada, *J. Phys. Chem.* C, 2012, 116, 24896–24901.
- 198 S. H. Kim, Y. J. Lee, D. H. Kim and Y. J. Lee, *ACS Appl. Mater. Interfaces*, 2018, **10**, 660–667.
- 199 Y. Cui, Y. Yue, G. Qian and B. Chen, *Chem. Rev.*, 2012, **112**, 1126–1162.
- 200 H.-Q. Yin and X.-B. Yin, Acc. Chem. Res., 2020, 53, 485-495.

201 L. K. Cadman, M. F. Mahon and A. D. Burrows, *Dalton Trans.*, 2018, 47, 2360-2367.

- 202 S. Wu, H. Min, W. Shi and P. Cheng, *Adv. Mater.*, 2020, 32, 1805871.
- 203 W. P. Lustig, S. Mukherjee, N. D. Rudd, A. V. Desai, J. Li and S. K. Ghosh, *Chem. Soc. Rev.*, 2017, **46**, 3242–3285.
- 204 B. Yan, Acc. Chem. Res., 2017, 50, 2789-2798.

Chemical Science

- 205 Y. Cui, F. Zhu, B. Chen and G. Qian, *Chem. Commun.*, 2015, 51, 7420–7431.
- 206 Y. Cui, H. Xu, Y. Yue, Z. Guo, J. Yu, Z. Chen, J. Gao, Y. Yang, G. Qian and B. Chen, *J. Am. Chem. Soc.*, 2012, **134**, 3979–3982.
- 207 S.-Y. Zhang, W. Shi, P. Cheng and M. J. Zaworotko, J. Am. Chem. Soc., 2015, 137, 12203–12206.
- 208 S. G. Dunning, A. J. Nuñez, M. D. Moore, A. Steiner, V. M. Lynch, J. L. Sessler, B. J. Holliday and S. M. Humphrey, *Chem*, 2017, 2, 579–589.
- 209 B. Liu, H. Shioyama, T. Akita and Q. Xu, J. Am. Chem. Soc., 2008, 130, 5390–5391.
- 210 B. Liu, X. Zhang, H. Shioyama, T. Mukai, T. Sakai and Q. Xu, *J. Power Sources*, 2010, **195**, 857–861.
- 211 Y. V. Kaneti, J. Tang, R. R. Salunkhe, X. Jiang, A. Yu, K. C. W. Wu and Y. Yamauchi, *Adv. Mater.*, 2016, 1604898.
- 212 L. Chen, L. Zhang, Z. Chen, H. Liu, R. Luque and Y. Li, *Chem. Sci.*, 2016, 7, 6015–6020.
- 213 H.-L. Jiang, B. Liu, Y.-Q. Lan, K. Kuratani, T. Akita, H. Shioyama, F. Zong and Q. Xu, J. Am. Chem. Soc., 2011, 133, 11854–11857.
- 214 A. Aijaz, N. Fujiwara and Q. Xu, *J. Am. Chem. Soc.*, 2014, **136**, 6790–6793.
- 215 W. Zhong, H. Liu, C. Bai, S. Liao and Y. Li, *ACS Catal.*, 2015, 5, 1850–1856.
- 216 X. Wang, J. Zhou, H. Fu, W. Li, X. Fan, G. Xin, J. Zheng and X. Li, *J. Mater. Chem. A*, 2014, 2, 14064–14070.
- 217 N. L. Torad, M. Hu, S. Ishihara, H. Sukegawa, A. A. Belik, M. Imura, K. Ariga, Y. Sakka and Y. Yamauchi, *Small*, 2014, 10, 2096–2107.
- 218 Y. Z. Chen, C. Wang, Z. Y. Wu, Y. Xiong, Q. Xu, S. H. Yu and H. L. Jiang, *Adv. Mater.*, 2015, 27, 5010–5016.
- 219 C.-C. Hou, L. Zou and Q. Xu, Adv. Mater., 2019, 31, 1904689.
- 220 Y. Yang, Z. Lun, G. Xia, F. Zheng, M. He and Q. Chen, *Energy Environ. Sci.*, 2015, **8**, 3563–3571.
- 221 J. Long, K. Shen, L. Chen and Y. Li, *J. Mater. Chem. A*, 2016, 4, 10254–10262.
- 222 D. Sun, L. Ye, F. Sun, H. García and Z. Li, *Inorg. Chem.*, 2017, 56, 5203–5209.
- 223 R. Das, P. Pachfule, R. Banerjee and P. Poddar, *Nanoscale*, 2012, **4**, 591–599.
- 224 X. F. Lu, Y. Chen, S. Wang, S. Gao and X. W. Lou, *Adv. Mater.*, 2019, **31**, 1902339.
- 225 J. Qian, T.-T. Li, Y. Hu and S. Huang, *Chem. Commun.*, 2017, 53, 13027–13030.
- 226 X. Li, X. Wang, J. Zhou, L. Han, C. Sun, Q. Wang and Z. Su, *J. Mater. Chem. A*, 2018, **6**, 5789–5796.
- 227 Y. Wang, W. Wu, Y. Rao, Z. Li, N. Tsubaki and M. Wu, *J. Mater. Chem. A*, 2017, **5**, 6170–6177.
- 228 X. F. Lu, L. Yu and X. W. Lou, Sci. Adv., 2019, 5, eaav6009.

- 229 T. Zhang, J. Du, P. Xi and C. Xu, ACS Appl. Mater. Interfaces, 2017, 9, 362-370.
- 230 Y. Lian, H. Sun, X. Wang, P. Qi, Q. Mu, Y. Chen, J. Ye, X. Zhao, Z. Deng and Y. Peng, *Chem. Sci.*, 2019, **10**, 464–474.
- 231 D. Cao, W. Kang, S. Wang, Y. Wang, K. Sun, L. Yang, X. Zhou, D. Sun and Y. Cao, *J. Mater. Chem. A*, 2019, 7, 8268–8276.
- 232 W. Hong, M. Kitta and Q. Xu, Small Methods, 2018, 2, 1800214.
- 233 J. Song, C. Zhu, B. Z. Xu, S. Fu, M. H. Engelhard, R. Ye, D. Du, S. P. Beckman and Y. Lin, *Adv. Energy Mater.*, 2017, 7, 1601555.
- 234 J.-c. Zheng, Y.-y. Yao, G.-q. Mao, H.-z. Chen, H. Li, L. Cao, X. Ou, W.-j. Yu, Z.-y. Ding and H. Tong, *J. Mater. Chem. A*, 2019, 7, 16479–16487.
- 235 H. Li, Y. Su, W. Sun and Y. Wang, *Adv. Funct. Mater.*, 2016, **26**, 8345–8353.
- 236 P. Yin, T. Yao, Y. Wu, L. Zheng, Y. Lin, W. Liu, H. Ju, J. Zhu, X. Hong, Z. Deng, G. Zhou, S. Wei and Y. Li, *Angew. Chem., Int. Ed.*, 2016, 55, 10800–10805.
- 237 H. Zhang, S. Hwang, M. Wang, Z. Feng, S. Karakalos, L. Luo, Z. Qiao, X. Xie, C. Wang, D. Su, Y. Shao and G. Wu, J. Am. Chem. Soc., 2017, 139, 14143–14149.
- 238 C. Yan, H. Li, Y. Ye, H. Wu, F. Cai, R. Si, J. Xiao, S. Miao, S. Xie, F. Yang, Y. Li, G. Wang and X. Bao, *Energy Environ. Sci.*, 2018, **11**, 1204–1210.
- 239 J. Li, M. Chen, D. A. Cullen, S. Hwang, M. Wang, B. Li, K. Liu, S. Karakalos, M. Lucero, H. Zhang, C. Lei, H. Xu, G. E. Sterbinsky, Z. Feng, D. Su, K. L. More, G. Wang, Z. Wang and G. Wu, *Nat. Catal.*, 2018, 1, 935–945.
- 240 Y.-N. Gong, L. Jiao, Y. Qian, C.-Y. Pan, L. Zheng, X. Cai, B. Liu, S.-H. Yu and H.-L. Jiang, *Angew. Chem., Int. Ed.*, 2020, **59**, 2705–2709.
- 241 J. Wang, Z. Huang, W. Liu, C. Chang, H. Tang, Z. Li, W. Chen, C. Jia, T. Yao, S. Wei, Y. Wu and Y. Li, *J. Am. Chem. Soc.*, 2017, 139, 17281–17284.
- 242 R. Wu, X. Qian, K. Zhou, J. Wei, J. Lou and P. M. Ajayan, *ACS Nano*, 2014, **8**, 6297–6303.
- 243 H. Li, M. Liang, W. Sun and Y. Wang, *Adv. Funct. Mater.*, 2016, **26**, 1098–1103.
- 244 C. Castillo-Blas, N. López-Salas, M. C. Gutiérrez, I. Puente-Orench, E. Gutiérrez-Puebla, M. L. Ferrer, M. Á. Monge and F. Gándara, *J. Am. Chem. Soc.*, 2019, **141**, 1766–1774.
- 245 S. Chen, M. Xue, Y. Li, Y. Pan, L. Zhu and S. Qiu, *J. Mater. Chem. A*, 2015, 3, 20145–20152.
- 246 G. Huang, L. Zhang, F. Zhang and L. Wang, *Nanoscale*, 2014, **6**, 5509–5515.
- 247 W. Guo, W. Sun and Y. Wang, ACS Nano, 2015, 9, 11462–11471.
- 248 X. Wang, L. Yu, B. Y. Guan, S. Song and X. W. Lou, *Adv. Mater.*, 2018, **30**, 1801211.
- 249 W. Liu, R. Yin, W. Shi, X. Xu, X. Shen, Q. Yin, L. Xu and X. Cao, *ACS Appl. Energy Mater.*, 2019, **2**, 579–586.
- 250 C. Qu, B. Zhao, Y. Jiao, D. Chen, S. Dai, B. M. deglee, Y. Chen, K. S. Walton, R. Zou and M. Liu, ACS Energy Lett., 2017, 2, 1263–1269.

Perspective

- 251 S. He, Z. Li, J. Wang, P. Wen, J. Gao, L. Ma, Z. Yang and S. Yang, RSC Adv., 2016, 6, 49478-49486.
- 252 H. Mei, Y. Mei, S. Zhang, Z. Xiao, B. Xu, H. Zhang, L. Fan, Z. Huang, W. Kang and D. Sun, Inorg. Chem., 2018, 57, 10953-10960.
- 253 X. Feng, H. Wang, X. Bo and L. Guo, ACS Appl. Mater. Interfaces, 2019, 11, 8018-8024.
- 254 Z.-F. Huang, J. Song, K. Li, M. Tahir, Y.-T. Wang, L. Pan, L. Wang, X. Zhang and J.-J. Zou, J. Am. Chem. Soc., 2016, 138, 1359-1365.
- 255 Q. Wang, Y. Luo, R. Hou, S. Zaman, K. Qi, H. Liu, H. S. Park and B. Y. Xia, Adv. Mater., 2019, 31, 1905744.
- 256 Q. Mao, J. Chen, H. Chen, Z. Chen, J. Chen and Y. Li, J. Mater. Chem. A, 2019, 7, 8472-8484.
- 257 J. Hao, W. Yang, Z. Zhang and J. Tang, Nanoscale, 2015, 7, 11055-11062.
- 258 L. Yan, L. Cao, P. Dai, X. Gu, D. Liu, L. Li, Y. Wang and X. Zhao, Adv. Funct. Mater., 2017, 27, 1703455.
- 259 Y. Du, M. Zhang, Z. Wang, Y. Liu, Y. Liu, Y. Geng and L. Wang, J. Mater. Chem. A, 2019, 7, 8602-8608.
- 260 Y. Du, Z. Li, Y. Liu, Y. Yang and L. Wang, Appl. Surf. Sci., 2018, 457, 1081-1086.
- 261 X. Xiao, C.-T. He, S. Zhao, J. Li, W. Lin, Z. Yuan, Q. Zhang, S. Wang, L. Dai and D. Yu, Energy Environ. Sci., 2017, 10, 893-899.
- 262 M. Lan, R.-M. Guo, Y. Dou, J. Zhou, A. Zhou and J.-R. Li, Nano Energy, 2017, 33, 238-246.
- 263 N. Tsumori, L. Chen, Q. Wang, Q.-L. Zhu, M. Kitta and Q. Xu, Chem, 2018, 4, 845-856.
- 264 Y. Shen, L.-W. Bao, F.-Z. Sun and T.-L. Hu, Mater. Chem. Front., 2019, 3, 2363-2373.
- 265 X. Wang, H. Xiao, A. Li, Z. Li, S. Liu, Q. Zhang, Y. Gong, L. Zheng, Y. Zhu, C. Chen, D. Wang, Q. Peng, L. Gu, X. Han, J. Li and Y. Li, J. Am. Chem. Soc., 2018, 140, 15336-15341.
- 266 X. Yang, J. Chen, J. Hu, S. Zhao, J. Zhao and X. Luo, Catal. Sci. Technol., 2018, 8, 573-579.
- 267 H. Huang, J.-R. Li, K. Wang, T. Han, M. Tong, L. Li, Y. Xie, Q. Yang, D. Liu and C. Zhong, Nat. Commun., 2015, 6, 8847.
- 268 J. Yang, F. Zhang, H. Lu, X. Hong, H. Jiang, Y. Wu and Y. Li, Angew. Chem., Int. Ed., 2015, 54, 10889-10893.
- 269 C. Rösler, A. Aijaz, S. Turner, M. Filippousi, A. Shahabi, W. Xia, G. Van Tendeloo, M. Muhler and R. A. Fischer, Chem. - Eur. J., 2016, 22, 3304-3311.
- 270 A. Li, K. Shen, J. Chen, Z. Li and Y. Li, Chem. Eng. Sci., 2017, **166**, 66-76.
- 271 B. N. Bhadra and S. H. Jhung, Nanoscale, 2018, 10, 15035-
- 272 L. Hu, R. Zhang, L. Wei, F. Zhang and Q. Chen, Nanoscale, 2015, 7, 450-454.
- 273 Y.-H. Qin, L. Huang, J.-X. Zheng and Q. Ren, Inorg. Chem. Commun., 2016, 72, 78-82.
- 274 L. Zhang, L. Shi, L. Huang, J. Zhang, R. Gao and D. Zhang, ACS Catal., 2014, 4, 1753-1763.
- 275 J. Zhang, B. An, Y. Hong, Y. Meng, X. Hu, C. Wang, J. Lin, W. Lin and Y. Wang, Mater. Chem. Front., 2017, 1, 2405-2409.

- 276 H. Chen, K. Shen, Q. Mao, J. Chen and Y. Li, ACS Catal., 2018, 8, 1417-1426.
- 277 L.-P. Yang, J.-L. Mi, H.-J. Wang, J.-H. Liang, X.-J. Yang, Y.-H. Feng, P. Zhang and L. Liu, ChemCatChem, 2020, 12,
- 278 Q. Wang, Z. Li, M. A. Bañares, L.-T. Weng, Q. Gu, J. Price, W. Han and K. L. Yeung, Small, 2019, 15, 1903525.
- 279 H. Jiang, C. Zhu, Y. Yuan, C. Yue, C. Ling, F. Liu and A. Li, Chem. Eng. J., 2020, 384, 123302.
- 280 S. Li, Y. Hou, Q. Chen, X. Zhang, H. Cao and Y. Huang, ACS Appl. Mater. Interfaces, 2020, 12, 2581-2590.
- 281 M. Yadav and Q. Xu, Energy Environ. Sci., 2012, 5, 9698-9725.
- 282 Q.-L. Zhu and Q. Xu, Energy Environ. Sci., 2015, 8, 478-512.
- 283 Z. Li and O. Xu, Acc. Chem. Res., 2017, 50, 1449-1458.
- 284 Q. Wang, L. Chen, Z. Liu, N. Tsumori, M. Kitta and Q. Xu, Adv. Funct. Mater., 2019, 29, 1903341.
- 285 M.-J. Chen, D.-X. Zhang, D. Li, S.-C. Ke, X.-C. Ma, G.-G. Chang, J. Chen and X.-Y. Yang, New J. Chem., 2020, 44, 3021-3027.
- 286 C.-C. Hou, Q.-Q. Chen, K. Li, C.-J. Wang, C.-Y. Peng, R. Shi and Y. Chen, J. Mater. Chem. A, 2019, 7, 8277-8283.
- 287 X.-L. Zhang, D.-X. Zhang, G.-G. Chang, X.-C. Ma, J. Wu, Y. Wang, H.-Z. Yu, G. Tian, J. Chen and X.-Y. Yang, Ind. Eng. Chem. Res., 2019, 58, 7209-7216.
- 288 X. Meng, C. Wan, Y. Wang and X. Ju, J. Alloys Compd., 2018, 735, 1637-1647.
- 289 P. Tan, G. Li, R. Fang, L. Chen, R. Luque and Y. Li, ACS Catal., 2017, 7, 2948-2955.
- 290 R. Fang, R. Luque and Y. Li, Green Chem., 2016, 18, 3152-3157.
- 291 S. Zhang, H. Ma, Y. Sun, Y. Luo, X. Liu, M. Zhang, J. Gao and J. Xu, Green Chem., 2019, 21, 1702–1709.
- 292 K. W. Golub, T. P. Sulmonetti, L. A. Darunte, M. S. Shealy and C. W. Jones, ACS Appl. Nano Mater., 2019, 2, 6040-6056.
- 293 H. Wang, X. Li, X. Lan and T. Wang, ACS Catal., 2018, 8, 2121-2128.
- 294 J. Zhu, F. Chen, Z. Zhang, M. Li, Q. Yang, Y. Yang, Z. Bao and Q. Ren, ACS Sustainable Chem. Eng., 2019, 7, 12955-12963.
- 295 H. Chen, K. Shen, Y. Tan and Y. Li, ACS Nano, 2019, 13, 7800-7810.
- 296 P. Mahata, T. Aarthi, G. Madras and S. Natarajan, J. Phys. Chem. C, 2007, 111, 1665-1674.
- 297 H. Chen, K. Shen, J. Chen, X. Chen and Y. Li, J. Mater. Chem. A, 2017, 5, 9937–9945.
- 298 B. Hu, J.-Y. Yuan, J.-Y. Tian, M. Wang, X. Wang, L. He, Z. Zhang, Z.-W. Wang and C.-S. Liu, J. Colloid Interface Sci., 2018, 531, 148-159.
- 299 Y. Xu, S. Wu, X. Li, Y. Huang, Z. Wang, Y. Han, J. Wu, H. Meng and X. Zhang, New J. Chem., 2017, 41, 15433-15438.
- 300 G. Liu, Y. Sheng, J. W. Ager, M. Kraft and R. Xu, EnergyChem, 2019, 1, 100014.
- 301 S. Zhang, H. Ye, J. Hua and H. Tian, EnergyChem, 2019, 1, 100015.

302 S. Li, J. Tan, Z. Jiang, J. Wang and Z. Li, *Chem. Eng. J.*, 2020, 384, 123354.

Chemical Science

- 303 J. Lu, J. Zhang, Q. Chen and H. Liu, *J. Photochem. Photobiol.*, *A*, 2019, **380**, 111853.
- 304 X. Tang, J.-H. Zhao, Y.-H. Li, Z.-J. Zhou, K. Li, F.-T. Liu and Y.-Q. Lan, *Dalton Trans.*, 2017, **46**, 10553–10557.
- 305 Y. Su, D. Ao, H. Liu and Y. Wang, J. Mater. Chem. A, 2017, 5, 8680–8689.
- 306 X. Zhao, J. Feng, J. Liu, W. Shi, G. Yang, G.-C. Wang and P. Cheng, *Angew. Chem., Int. Ed.*, 2018, 57, 9790–9794.
- 307 B. Ma, T.-T. Chen, Q.-Y. Li, H.-N. Qin, X.-Y. Dong and S.-Q. Zang, *ACS Appl. Energy Mater.*, 2019, 2, 1134–1148.
- 308 W. Chen, J. Fang, Y. Zhang, G. Chen, S. Zhao, C. Zhang, R. Xu, J. Bao, Y. Zhou and X. Xiang, *Nanoscale*, 2018, 10, 4463–4474.
- 309 T. Wang, L. Shi, J. Tang, V. Malgras, S. Asahina, G. Liu, H. Zhang, X. Meng, K. Chang, J. He, O. Terasaki, Y. Yamauchi and J. Ye, *Nanoscale*, 2016, **8**, 6712–6720.
- 310 Q. Mu, W. Zhu, G. Yan, Y. Lian, Y. Yao, Q. Li, Y. Tian, P. Zhang, Z. Deng and Y. Peng, *J. Mater. Chem. A*, 2018, **6**, 21110–21119.
- 311 H. Jiang, S. Gong, S. Xu, P. Shi, J. Fan, V. Cecen, Q. Xu and Y. Min, *Dalton Trans.*, 2020, **49**, 5074–5086.
- 312 S. Chen, J. Yu and J. Zhang, J. CO2 Util., 2018, 24, 548-554.
- 313 H.-F. Wang, L. Chen, H. Pang, S. Kaskel and Q. Xu, *Chem. Soc. Rev.*, 2020, **49**, 1414–1448.
- 314 S. Zhu, J. Ge, C. Liu and W. Xing, *EnergyChem*, 2019, 1, 100018.
- 315 H.-F. Wang and Q. Xu, Matter, 2019, 1, 565-595.
- 316 Q. Ren, H. Wang, X.-F. Lu, Y.-X. Tong and G.-R. Li, *Adv. Sci.*, 2018, 5, 1700515.
- 317 H. Zhang, H. Osgood, X. Xie, Y. Shao and G. Wu, *Nano Energy*, 2017, **31**, 331–350.
- 318 X. Han, X. Ling, Y. Wang, T. Ma, C. Zhong, W. Hu and Y. Deng, *Angew. Chem.*, *Int. Ed.*, 2019, **58**, 5359–5364.
- 319 L. Du, L. Luo, Z. Feng, M. Engelhard, X. Xie, B. Han, J. Sun, J. Zhang, G. Yin, C. Wang, Y. Wang and Y. Shao, *Nano Energy*, 2017, 39, 245–252.
- 320 J. Zhou, Y. Dou, A. Zhou, L. Shu, Y. Chen and J.-R. Li, *ACS Energy Lett.*, 2018, 3, 1655–1661.
- 321 H. Xu, Z.-X. Shi, Y.-X. Tong and G.-R. Li, *Adv. Mater.*, 2018, **30**, 1705442.
- 322 X. Wang, L. Chai, J. Ding, L. Zhong, Y. Du, T.-T. Li, Y. Hu, J. Qian and S. Huang, *Nano Energy*, 2019, **62**, 745–753.
- 323 Q. Shi, S. Fu, C. Zhu, J. Song, D. Du and Y. Lin, *Mater. Horiz.*, 2019, **6**, 684–702.
- 324 Y. Qian, I. A. Khan and D. Zhao, Small, 2017, 13, 1701143.
- 325 X. Li, L. Yang, T. Su, X. Wang, C. Sun and Z. Su, *J. Mater. Chem. A*, 2017, 5, 5000–5006.
- 326 X.-Y. Yu, Y. Feng, Y. Jeon, B. Guan, X. W. Lou and U. Paik, *Adv. Mater.*, 2016, **28**, 9006–9011.
- 327 B. Zhu, R. Zou and Q. Xu, Adv. Energy Mater., 2018, 8, 1801193.
- 328 W. Ahn, M. G. Park, D. U. Lee, M. H. Seo, G. Jiang, Z. P. Cano, F. M. Hassan and Z. Chen, *Adv. Funct. Mater.*, 2018, **28**, 1802129.

- 329 Y. Pan, K. Sun, S. Liu, X. Cao, K. Wu, W.-C. Cheong, Z. Chen, Y. Wang, Y. Li, Y. Liu, D. Wang, Q. Peng, C. Chen and Y. Li, J. Am. Chem. Soc., 2018, 140, 2610–2618.
- 330 B. Zhu, D. Xia and R. Zou, *Coord. Chem. Rev.*, 2018, 376, 430–448.
- 331 L. Li, Y. Huang and Y. Li, EnergyChem, 2020, 2, 100024.
- 332 W. Guo, X. Sun, C. Chen, D. Yang, L. Lu, Y. Yang and B. Han, *Green Chem.*, 2019, 21, 503-508.
- 333 X. Wang, Z. Chen, X. Zhao, T. Yao, W. Chen, R. You, C. Zhao, G. Wu, J. Wang, W. Huang, J. Yang, X. Hong, S. Wei, Y. Wu and Y. Li, *Angew. Chem.*, *Int. Ed.*, 2018, 57, 1944–1948.
- 334 R. Zhao, H. Xie, L. Chang, X. Zhang, X. Zhu, X. Tong, T. Wang, Y. Luo, P. Wei, Z. Wang and X. Sun, *EnergyChem*, 2019, 1, 100011.
- 335 S. Chen, H. Jang, J. Wang, Q. Qin, X. Liu and J. Cho, *J. Mater. Chem. A*, 2020, **8**, 2099–2104.
- 336 A. Indra, T. Song and U. Paik, *Adv. Mater.*, 2018, **30**, 1705146.
- 337 H. B. Wu and X. W. Lou, Sci. Adv., 2017, 3, eaap9252.
- 338 Y. Li, Y. Xu, W. Yang, W. Shen, H. Xue and H. Pang, *Small*, 2018, **14**, 1704435.
- 339 X. Cao, C. Tan, M. Sindoro and H. Zhang, *Chem. Soc. Rev.*, 2017, **46**, 2660–2677.
- 340 R. R. Salunkhe, Y. V. Kaneti and Y. Yamauchi, *ACS Nano*, 2017, 11, 5293–5308.
- 341 S. Chen, M. Xue, Y. Li, Y. Pan, L. Zhu, D. Zhang, Q. Fang and S. Qiu, *Inorg. Chem. Front.*, 2015, 2, 177–183.
- 342 R. R. Salunkhe, Y. V. Kaneti, J. Kim, J. H. Kim and Y. Yamauchi, *Acc. Chem. Res.*, 2016, **49**, 2796–2806.
- 343 M. S. Javed, H. Lei, J. Li, Z. Wang and W. Mai, *J. Mater. Chem. A*, 2019, 7, 17435–17445.
- 344 M. Yi, C. Zhang, C. Cao, C. Xu, B. Sa, D. Cai and H. Zhan, *Inorg. Chem.*, 2019, **58**, 3916–3924.
- 345 M. K. Aslam, S. S. Ahmad Shah, M. S. Javed, S. Li, S. Hussain, B. Hu, N. A. Khan and C. Chen, *J. Electroanal. Chem.*, 2019, 855, 113615.
- 346 C. Young, J. Kim, Y. V. Kaneti and Y. Yamauchi, *ACS Appl. Energy Mater.*, 2018, **1**, 2007–2015.
- 347 T. Huang, X.-Z. Song, X. Chen, X.-L. Chen, F.-F. Sun, Q.-F. Su, L.-D. Li and Z. Tan, *New J. Chem.*, 2018, **42**, 5128–5134.
- 348 W. Lu, J. Shen, P. Zhang, Y. Zhong, Y. Hu and X. W. Lou, *Angew. Chem., Int. Ed.*, 2019, **58**, 15441–15447.
- 349 D. P. Dubal, K. Jayaramulu, J. Sunil, Š. Kment, P. Gomez-Romero, C. Narayana, R. Zbořil and R. A. Fischer, *Adv. Funct. Mater.*, 2019, **29**, 1900532.
- 350 G. Zou, H. Hou, P. Ge, Z. Huang, G. Zhao, D. Yin and X. Ji, *Small*, 2018, **14**, 1702648.
- 351 X. Zhang, P. Dong and M.-K. Song, *Batteries Supercaps*, 2019, 2, 591–626.
- 352 J. Zhang, L. Wang, L. Xu, X. Ge, X. Zhao, M. Lai, Z. Liu and W. Chen, *Nanoscale*, 2015, 7, 720–726.
- 353 H. Guo, T. Li, W. Chen, L. Liu, X. Yang, Y. Wang and Y. Guo, *Nanoscale*, 2014, **6**, 15168–15174.
- 354 Y. Xia, B. Wang, G. Wang, X. Liu and H. Wang, *ChemElectroChem*, 2016, 3, 299–308.

355 L. Hou, L. Lian, L. Zhang, G. Pang, C. Yuan and X. Zhang,

Perspective

- Adv. Funct. Mater., 2015, 25, 238-246.
 356 J. Ma, H. Wang, X. Yang, Y. Chai and R. Yuan, J. Mater. Chem. A, 2015, 3, 12038-12043.
- 357 J. Wu, Y. Song, R. Zhou, S. Chen, L. Zuo, H. Hou and L. Wang, *J. Mater. Chem. A*, 2015, 3, 7793–7798.
- 358 F. Zou, X. Hu, Z. Li, L. Qie, C. Hu, R. Zeng, Y. Jiang and Y. Huang, *Adv. Mater.*, 2014, **26**, 6622–6628.
- 359 M. K. Aslam, S. S. A. Shah, S. Li and C. Chen, *J. Mater. Chem. A*, 2018, **6**, 14083–14090.
- 360 W. C. Haoying Yang, Y. Han and B. Wang, *Chin. Chem. Lett.*, 2018, **29**, 842–844.

- 361 X. Zhang, D. Li, G. Zhu, T. Lu and L. Pan, *J. Colloid Interface Sci.*, 2017, **499**, 145–150.
- 362 G. Fang, J. Zhou, Y. Cai, S. Liu, X. Tan, A. Pan and S. Liang, *J. Mater. Chem. A*, 2017, **5**, 13983–13993.
- 363 J. Li, D. Wang, J. Zhou, L. Hou and F. Gao, *ChemElectroChem*, 2019, **6**, 917–927.
- 364 J. Tang, S. Wu, T. Wang, H. Gong, H. Zhang, S. M. Alshehri, T. Ahamad, H. Zhou and Y. Yamauchi, *ACS Appl. Mater. Interfaces*, 2016, **8**, 2796–2804.
- 365 W. Yin, Y. Shen, F. Zou, X. Hu, B. Chi and Y. Huang, *ACS Appl. Mater. Interfaces*, 2015, 7, 4947–4954.