

PAPER

[View Article Online](#)
[View Journal](#) | [View Issue](#)Cite this: *Nanoscale Adv.*, 2020, 2, 2099

One-step facile synthesis of nickel–chromium layered double hydroxide nanoflakes for high-performance supercapacitors†

Zuo Chen,^{‡a} Hao Deng,^{‡a} Man Zhang,^a Zhiyu Yang,^a Di Hu,^a Yuchen Wang^a and Kai Yan^{‡ab}

Rational design and synthesis of efficient electrodes with pronounced energy storage properties are crucial for supercapacitors. Herein, we report thin NiCr-layered double hydroxide nanoflakes (NiCr-LDNs) for a high-performance supercapacitor. These fabricated NiCr-LDNs, with various Ni²⁺/Cr³⁺ ratios, are one-step controllably synthesized through ultrasonication coupled with mechanical agitation, without hydrothermal treatment or extra exfoliation using organic solvents. Through comparison of different Ni²⁺/Cr³⁺ ratios, the Ni₂Cr₁-LDNs with a 4.7 nm thickness exhibited a superb capacitance performance of 1525 F g^{−1} at 2 A g^{−1}, which is competitive with most previously reported layered double hydroxide (LDH)-based electrodes. These thin nanoflake structures have the potential to reduce the energy barrier and enhance the capture ability of electrolyte ions. Besides, an asymmetric supercapacitor (ASC) assembled using Ni₂Cr₁-LDNs achieved a remarkable energy density of 55.22 W h kg^{−1} at a power density of 400 W kg^{−1} and maintained high specific capacitance (over 81%), even after 5000 cycles. This work offers an efficient and facile route to fabricating LDH nanoflakes for boosting energy storage capabilities.

Received 3rd March 2020

Accepted 1st April 2020

DOI: 10.1039/d0na00178c

rsc.li/nanoscale-advances

Introduction

Layered double hydroxides (LDHs), also called hydrotalcite-like materials, are a family of two-dimensional anionic compounds formed by the orderly arrangement of anions between layers and positively charged laminates.^{1,2} The formula of LDHs is expressed as follows: M_{1−x}²⁺M_x³⁺(OH)₂(A^{n−})_{x/n}·mH₂O, where M²⁺, M³⁺ and A^{n−} represent divalent metal ions, trivalent metal ions and intercalated anions, respectively.^{1–6} LDHs are alkaline and thermally stable, can exchange anions, and have a controllable composition and structure.^{7–9} On the one hand, the unique

spatial structure of LDHs provides a large surface area to transfer charge and capture electrons.^{8,10} On the other hand, the high dispersion of variable valence metal ions on the lamella can provide abundant electrochemically active sites, resulting in high pseudocapacitance.^{11–13} Over the past few decades, LDHs have attracted considerable attention for use as electrochemical supercapacitors. For example, Liu *et al.* fabricated NiO/NiMn-LDHs by a facile two-step approach and reported a specific capacitance of 937 F g^{−1} at a current density of 0.5 A g^{−1}.¹⁴ Li *et al.* fabricated NiFe-LDHs/graphene for use as a supercapacitor with a good specific capacitance of 1462.5 F g^{−1} at 5 A g^{−1}.¹⁵ Zhang *et al.* synthesized a NiAl-LDH pseudo-capacitor electrode, which exhibited a specific capacitance of 1.040 C cm^{−2} at 1.68 mA cm^{−2}.¹⁶

However, LDHs still have their own intrinsic shortcomings, for example, the accumulation of layers and the blocked inter-layer space limit electrolyte ion access to internal active sites.^{17,18} In order to facilitate the diffusion of ions and enhance electronic conductivity, researchers have developed several fabrication strategies to reduce the thickness of layers and increase the distance between layers. One of the most common methods is chemical stripping. In a pioneering study, Hu *et al.* investigated the synthesis of CoCo-, NiFe- and NiCo-LDH nanosheets by dispersing LDH powder into 100 mL of formamide and stirring for 24 h.¹⁹ Zhong *et al.* studied the exfoliation of CoAl-LDHs by stirring for 2 days in formamide.²⁰ Du *et al.* synthesized NiAl-LDHs in a formamide solution by stirring for 3 days

^aSchool of Environmental Science and Engineering, Sun Yat-sen University, 135 Xingang Xi Road, Guangzhou 510275, P. R. China. E-mail: yank9@mail.sysu.edu.cn

^bGuangdong Provincial Key Laboratory of Environmental Pollution Control and Remediation Technology, Guangzhou 510275, P. R. China

† Electronic supplementary information (ESI) available: XRD patterns of Ni₃Cr₁-LDNs, Ni₂Cr₁-LDNs, Ni₁Cr₁-LDNs, Ni₁Cr₂-LDNs and Ni₂Cr₁-LDHs; SEM images of the synthesized Ni₂Cr₁-LDHs and Ni₂Cr₁-LDNs; SEM image of the Ni₂Cr₁-LDNs and the corresponding EDS mapping images of O, Cr and Ni elements; AFM image and the corresponding height profile of Ni₁Cr₁-LDNs; transmission electron microscopy image of Ni₁Cr₁-LDNs; and N₂ adsorption/desorption isotherms of Ni₁Cr₁-LDNs, Ni₂Cr₁-LDNs and Ni₃Cr₁-LDNs. CV curves of Ni₂Cr₁-LDNs and pure nickel foam, CV curves of Ni₂Cr₁-LDNs, Ni(OH)₂ and Cr(OH)₃, GCD curves of Ni₂Cr₁-LDNs, Ni(OH)₂ and Cr(OH)₃, GCD curves of Ni₂Cr₁-LDNs at various current densities from 2 to 10 A g^{−1}, CV curves of AC at scan rates from 5 to 50 mV s^{−1}, and GCD curves of AC at various current densities from 1 to 10 A g^{−1}. See DOI: 10.1039/d0na00178c

‡ These authors contributed equally to this work.

under nitrogen protection.²⁰ In addition, some new exfoliation methods (*e.g.*, Ar-plasma, nitrogen-plasma, and solid-phase exfoliation techniques) were used to synthesize thin LDHs.^{17,22,23} Our previous studies have also shown that ultrasonication-assisted hydrothermal synthesis is a good approach to fabricate thin CoMn-LDHs and NiCo-LDHs in several steps, enhancing the catalytic performance of oxygen evolution in comparison with bulk LDH precursors.^{17,24} However, these exfoliation methods still have several steps and, therefore, suffer from low efficiency and complexity, are time-consuming and require a large amount of chemical reagents. Besides, the energy storage performance and durability of the previously reported LDHs still need to be improved.^{17,24} Developing a one-step, facile method to fabricate thin LDHs with a controllable morphology for boosting energy storage capacity is still a challenge.

Inspired by the advanced studies, we endeavored to control the synthesis of thin NiCr-layered double hydroxide nanoflakes (NiCr-LDNs) with different $\text{Ni}^{2+}/\text{Cr}^{3+}$ ratios in one step, and these fabricated LDNs served as a superior pseudocapacitive electrode for energy storage. This alternative construction strategy shows great potential for the large-scale production of nanoflakes. Several types of NiCr-LDNs with different $\text{Ni}^{2+}/\text{Cr}^{3+}$ ratios were successfully designed and evaluated with electrochemical tests. The Ni_2Cr_1 -LDN electrode achieved a remarkable specific capacitance of 1525 F g^{-1} at a current density of 2 A g^{-1} in a 6 M KOH electrolyte using the three-electrode system. Besides, the Ni_2Cr_1 -LDNs were used as a positive electrode to assemble an asymmetric supercapacitor, which provided a relatively outstanding energy density of $55.22 \text{ W h kg}^{-1}$ at a power density of 400 W kg^{-1} , retaining 81.1% of the original specific capacitance even after 5000 cycles. Furthermore, Ni_2Cr_1 -LDNs exhibited low resistance, fast kinetics and long durability. This work provides a facile and efficient way to fabricate LDH nanoflakes to largely enhance capacitance.

Experimental

Synthesis of NiCr-LDNs

All of the chemicals were used without any purification. Nickel chloride hexahydrate ($\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$), chromium chloride hexahydrate ($\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$), sodium hydroxide (NaOH), and sodium carbonate (Na_2CO_3) were bought from Macklin Chemical Reagent Co. Ltd. The general synthesis procedure is depicted in Fig. 1. $\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$ and $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ were dissolved in distilled water to prepare 1 M aqueous solutions. Then, NiCl_2 (1 M) and CrCl_3 (1 M) were added to a beaker to achieve mixed solution A (10 mL , the molar ratios of Ni^{2+} and Cr^{3+} in solution A ranged from $3:1$ to $1:2$). Solution A was mechanically stirred (200 rpm) and ultrasonicated (40 kHz) simultaneously. About 0.2 mol of Na_2CO_3 and 0.8 mol of NaOH were dissolved in distilled water (1 L), and then the mixture (solution B) was slowly titrated into solution A to adjust the pH to 8.5 and held for 1 h . After centrifugation and vacuum drying at 50°C for 14 h , the powder products were collected and denoted as Ni_3Cr_1 -LDNs, Ni_2Cr_1 -LDNs, Ni_1Cr_1 -LDNs, and Ni_1Cr_2 -LDNs

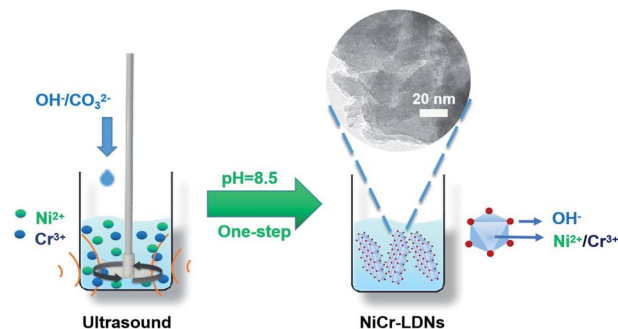


Fig. 1 Schematic illustration of the facile synthesis of NiCr-LDNs in one-step.

corresponding to a $\text{Ni}^{2+}/\text{Cr}^{3+}$ ratio of $3:1$, $2:1$, $1:1$, and $1:2$, respectively. The reference Ni_2Cr_1 -LDHs were synthesized in the same way without ultrasonic treatment.

Electrode characterization

X-ray diffraction (XRD) characterization was conducted on a D/max-2200vpc (Rigaku, Japan) at 40 kV and 26 mA with $\text{Cu K}\alpha_1$ radiation of 1.54060 \AA . The 2θ degree ranged from 5° to 70° , and the scan rate was $10^\circ \text{ min}^{-1}$. Transmission electron microscopy (TEM) was used to identify the microstructure and the morphologies of the samples (coated on Cu grids) and was performed using a JEM-2100F (JEOL, Japan) operated at 200 kV . Scanning electron microscopy (SEM, ZEISS, SIGMA 500, GER) and corresponding energy-dispersive X-ray spectrometry (EDS, Bruker, GER) were used to characterize the microstructures and element distribution of the products at 10 kV . X-ray photoelectron spectroscopy (XPS) analysis was carried out using an ESCALab 250 imaging X-ray photoelectron spectrometer system (Thermo Scientific, USA) with monochromatic $\text{Al K}\alpha$ X-rays as the excitation source ($E = 1486.6 \text{ eV}$) and a pass energy of 20 eV . Atomic force microscopy (AFM) was used to obtain the thickness of samples and was performed on a Dimension Edge (Bruker, USA) in tapping mode. For AFM, the samples were dispersed in an ethanol solvent and dripped onto a mica plate for testing. N_2 adsorption-desorption isotherms of the samples were analyzed by using a Micromeritics ASAP 2020 nitrogen adsorption apparatus (USA) at 77 K , whereas the physical activation was performed at 150°C for 10 h before measurements. The specific surface area was obtained from the adsorption isotherm curve. Pore size distributions were calculated using the Barrett-Joyner-Halenda (BJH) method, for both the adsorption and desorption curves. The total volume was estimated from the adsorbed amount at a relative pressure P/P_0 of 0.995 .

Electrochemical characterization and tests

Galvanostatic charge-discharge (GCD), cyclic voltammetry (CV) and electrochemical impedance spectroscopy (EIS) tests of the samples were conducted using a CHI760E electrochemical workstation with an alkaline electrolyte (6 M KOH) in a three-electrode system. A platinum filament (CHI115) and saturated



calomel electrode (SCE, CHI150) worked as the counter and reference electrodes, respectively. Then 70 wt% active materials, a 15 wt% polytetrafluoroethylene emulsion (PTFE, Aladdin) and 15 wt% supercarbon (Alfa Aesar) were mixed to prepare the working electrode. The mixture was then stirred and pressed onto nickel foam (1 cm²) under 10 MPa and dried at 70 °C for 12 h. The loaded mass of the active material was controlled at 3–4 mg cm⁻². The specific capacitance of the electrode material was calculated using the formula:^{25,26}

$$C = \frac{I \times \Delta t}{m \times \Delta V}, \quad (1)$$

where I , ΔV , Δt , and m represent the discharge current (A), the voltage window (V), the discharge time (s) and the quantity of the active material (g), respectively.

Assembly and test of the asymmetric supercapacitor

The asymmetric supercapacitor was fabricated using Ni₂Cr₁-LDNs as the positive electrode, active carbon (AC, Kuraray) as the negative electrode, and cellulose paper as the separator in a 6 M KOH electrolyte. The preparation of the AC electrode was similar to that of the Ni₂Cr₁-LDN electrode. The energy density (E , Wh kg⁻¹) and power density (P , W kg⁻¹) of Ni₂Cr₁-LDNs//AC were estimated according to the following equations:^{15,21}

$$E = \frac{C \times \Delta V^2}{2 \times 3.6} \quad (2)$$

$$P = \frac{3600 \times E}{\Delta t}, \quad (3)$$

where ΔV , Δt and C represent the potential window (V), the discharge time (s) and the capacitance (F g⁻¹), respectively.

Results and discussion

Structural and morphological characterization

The crystal structures of the five materials with different Ni²⁺/Cr³⁺ ratios were identified by powder X-ray diffraction. Fig. S1† shows a series of crystal planes (003), (006), (012) and (110) of the Ni₂Cr₁-LDN samples at 11°, 23°, and 35° that were indexed to the characteristic peaks of LDHs synthesized without ultrasonication (PDF#89-7111). In the one-step synthesis by ultrasonication coupled with mechanical stirring, the typical layers of LDHs were exfoliated into thin nanoflakes with lower intensity and broader peaks, as indicated by the XRD patterns.^{27–29}

Fig. S2† presents the morphology differences between the Ni₂Cr₁-LDHs and Ni₂Cr₁-LDNs by SEM. After the ultrasonication treatment, brucite-like layers of Ni₂Cr₁-LDHs were exfoliated into fragments with thin nanoflakes. The structure with thin nanoflakes could facilitate the diffusion of electrolyte ions into internal active sites to provide significant capacitance. Moreover, the corresponding EDS mapping confirmed that the Ni and Cr elements were well dispersed in Ni₂Cr₁-LDNs (Fig. S3†), showing the effect of ultrasonication during co-precipitation.

AFM is a technique used to directly measure the thickness, as shown in Fig. 2, S4 and S5.† A thickness of 4.77 nm for Ni₂Cr₁-LDN single layer was measured, while, in comparison,

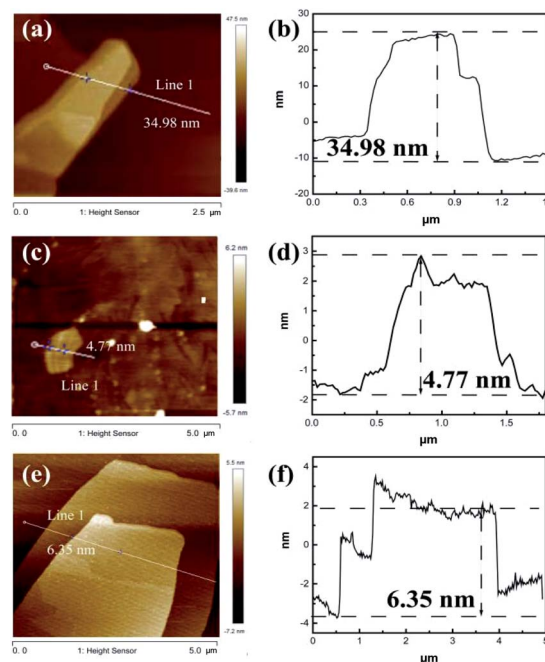


Fig. 2 AFM images and height profile of (a and b) Ni₂Cr₁-LDHs, (c and d) Ni₂Cr₁-LDNs, and (e and f) Ni₃Cr₁-LDNs.

the Ni₂Cr₁-LDHs synthesized without ultrasonication had a thickness of 34.98 nm, confirming the important role of ultrasonication in producing nanoflakes. Different NiCr-LDN nanoflakes with various Ni²⁺/Cr³⁺ ratios were also synthesized under identical conditions. Ni₁Cr₁-LDNs (Fig. S5†) and Ni₃Cr₁-LDNs (Fig. 2e and f) had 16.61 nm and 6.35 nm thicknesses, respectively. A TEM study was further conducted to analyze the microstructure of the as-prepared samples. From Fig. 3, it is clear that bulk Ni₂Cr₁-LDHs had several stacked layers, while

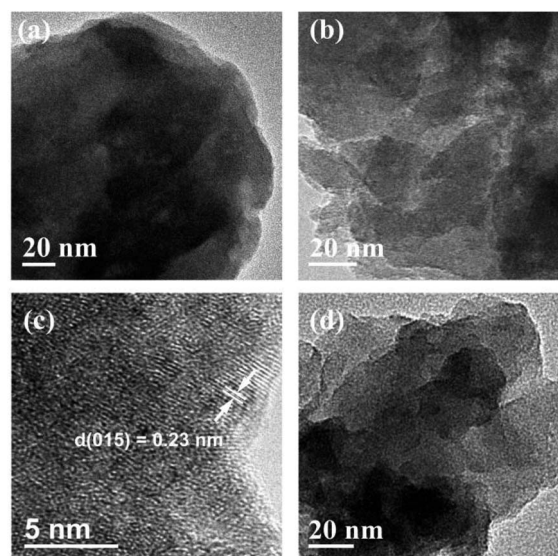


Fig. 3 TEM images of (a) Ni₂Cr₁-LDHs, (b and c) Ni₂Cr₁-LDNs and (d) Ni₃Cr₁-LDNs.



the $\text{Ni}_2\text{Cr}_1\text{-LDN}$ nanoflakes were successfully synthesized with thin layers (Fig. 3b). Besides, a typical lattice spacing of 0.20 nm was indexed to the (107) plane of $\text{Ni}_2\text{Cr}_1\text{-LDNs}$ (PDF#89-7111).^{30,31} By comparing $\text{Ni}_3\text{Cr}_1\text{-LDNs}$ (Fig. 3d) with $\text{Ni}_1\text{Cr}_1\text{-LDNs}$ (Fig. S6†), it was further confirmed that ultrasonication could efficiently peel off the bulk LDH structure and form nanoflakes. According to Table S1 and Fig. S7,† the specific surface areas of $\text{Ni}_1\text{Cr}_1\text{-LDNs}$, $\text{Ni}_1\text{Cr}_1\text{-LDNs}$ and $\text{Ni}_1\text{Cr}_1\text{-LDNs}$ were 62.5, 73.4, and 63.3 $\text{m}^2 \text{g}^{-1}$, respectively. The total pore volumes of $\text{Ni}_1\text{Cr}_1\text{-LDNs}$, $\text{Ni}_1\text{Cr}_1\text{-LDNs}$ and $\text{Ni}_1\text{Cr}_1\text{-LDNs}$ were 0.065, 0.073, and 0.068 $\text{cm}^3 \text{g}^{-1}$, respectively. The nanoflake structure provides a larger surface area and allows the flow of ions between laminates, which is favorable for energy storage.^{30,31}

XPS was further conducted to analyze the chemical state and composition of $\text{Ni}_2\text{Cr}_1\text{-LDNs}$. Fig. 4a shows the survey scan of the $\text{Ni}_2\text{Cr}_1\text{-LDNs}$, in which Ni, Cr, O and C elements existed. Fig. 4b illustrates that the O element is mainly in the form of $\text{Ni}(\text{OH})_2$ (531.5 eV).³² The O 1s lattice oxides for $\text{Cr}(\text{OH})_3$ and Cr_2O_3 were not distinguished due to the overlap of Ni^{2+} and Cr^{3+} .³² From the split spin-orbit peaks of Cr 2p in Fig. 4c, it was observed that $\text{Cr}(\text{OH})_3$ can be fitted with a single $2p_{3/2}$ peak at 577.0 eV, and a corresponding $2p_{1/2}$ peak located at 586.9 eV.³³ A lower peak at 578.9 eV was attributed to the partial oxidation of Cr^{3+} . Typical Ni $2p_{3/2}$ peaks for $\text{Ni}(\text{OH})_2$ were fitted with the main peak (855.5 eV) and the secondary peak (856.3 eV).^{32–35} A satellite peak for Ni $2p_{3/2}$ was obviously displayed at 861.6 eV (Fig. 4d).³²

Electrochemical evaluation

The electrochemical properties of the samples were investigated through CV, GCD, and EIS. In order to study the capacitive performance of the NiCr-LDN electrodes, CV and GCD curves of the pure nickel foam electrode, $\text{Cr}(\text{OH})_3$ electrode, $\text{Ni}(\text{OH})_2$ electrode, and NiCr-LDN electrode are shown in Fig. S8a–c.† Obvious redox peaks were observed in the CV curves of the $\text{Ni}(\text{OH})_2$ electrode and the NiCr-LDN electrode. The equilibrium

potential of the redox peaks was 0.3–0.4 V vs. SCE, which could be the faradaic redox reaction of $\text{Ni}(\text{OH})_2$ as follows:^{36,37}



The result indicates that $\text{Ni}(\text{OH})_2$ contributed most to the capacitance of the NiCr-LDN electrode, whereas pure nickel foam and $\text{Cr}(\text{OH})_3$ contributed very little. Furthermore, compared with the $\text{Ni}(\text{OH})_2$ electrode, the higher current density of the redox peaks of the NiCr-LDN electrode clearly demonstrates that interactions between Ni and Cr could improve the electrochemical performance. According to Fig. S8c,† the specific capacitance of the $\text{Ni}_2\text{Cr}_1\text{-LDN}$ electrode was 1525 F g^{-1} , which was higher than that of the $\text{Ni}(\text{OH})_2$ electrode (812 F g^{-1}).

The CV curves of the $\text{Ni}_2\text{Cr}_1\text{-LDN}$, $\text{Ni}_3\text{Cr}_1\text{-LDN}$, $\text{Ni}_1\text{Cr}_1\text{-LDN}$, $\text{Ni}_1\text{Cr}_2\text{-LDN}$, and $\text{Ni}_2\text{Cr}_1\text{-LDH}$ electrodes at 10 mV s^{-1} in the potential range of −0.2 to 0.6 V are compared in Fig. 5a. Notably, $\text{Ni}_2\text{Cr}_1\text{-LDNs}$ exhibited much higher redox peaks than the other four samples, illustrating that $\text{Ni}_2\text{Cr}_1\text{-LDNs}$ possess the highest specific capacitance. In addition, the reduction peak of $\text{Ni}_2\text{Cr}_1\text{-LDNs}$ shifted to a lower potential due to the stacking of layers, which affects the transfer of ions and charge.³⁸ Fig. 5b displays the CV curves of $\text{Ni}_2\text{Cr}_1\text{-LDNs}$ at various scan rates. The anodic peak shifted to a positive potential and the cathodic peak shifted to a negative potential as the scan rate increased because the $\text{Ni}_2\text{Cr}_1\text{-LDN}$ electrode is quasi-reversible and polarizable. According to the CV curves, the apparent heterogeneous electron transfer rate constant (k_s) was estimated using the formula:^{39,40}

$$\log k_s = a \log(1 - a) + (1 - a) \log a - \log \frac{RT}{nFv} - \frac{a(1 - a)nF\Delta E_p}{2.303RT} \quad (5)$$

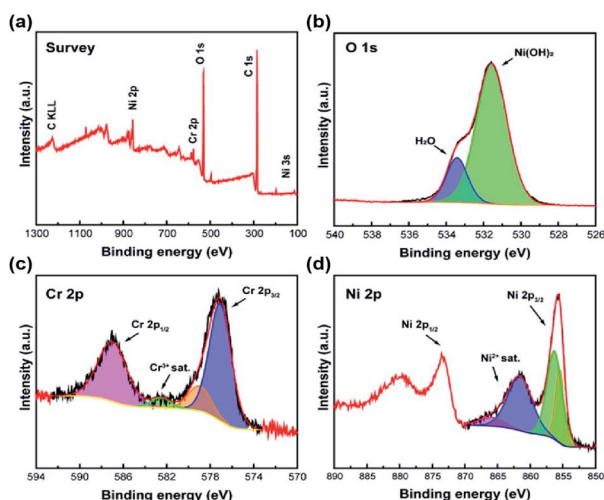


Fig. 4 XPS spectra of $\text{Ni}_2\text{Cr}_1\text{-LDNs}$: survey (a), and fitting spectra of O 1s (b), Cr 2p (c) and Ni 2p (d).

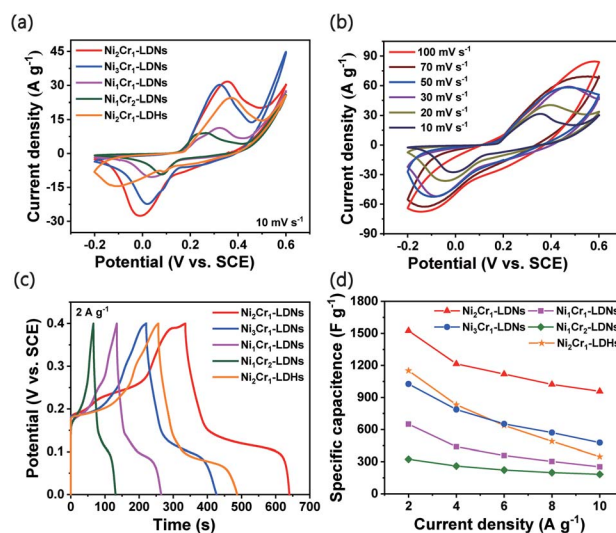


Fig. 5 (a) CV curves of LDN and LDH electrodes at a scan rate of 10 mV s^{-1} , (b) CV curves of $\text{Ni}_2\text{Cr}_1\text{-LDNs}$ at various scan rates from 5 to 100 mV s^{-1} , (c) GCD curves of LDNs and LDHs at a current density of 2 A g^{-1} , and (d) specific capacitances of LDN and LDH electrodes at different current densities.



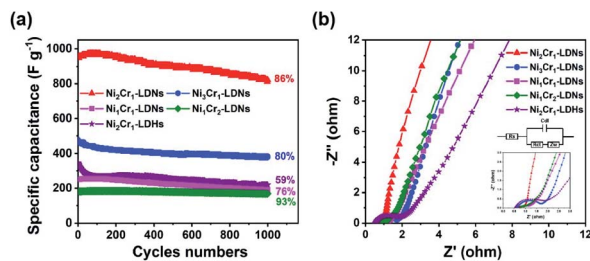


Fig. 6 (a) Cycle stability of LDN and LDH electrodes at 10 A g⁻¹, and (b) Nyquist plots of LDN and LDH electrodes.

where ΔE_p is the peak potential separation, n represents the number of electrons transferred in the faradaic reaction, v represents the scan rate, and T , R , F , and a represent constants. The average k_s value of the Ni₂Cr₁-LDN electrode was 0.595 cm s⁻¹, which is higher than that of the Ni₂Cr₁-LDH electrode (0.307 cm s⁻¹). These results indicated that exfoliation of the layered structure contributed to fast ion transfer.

Fig. 5c gives the GCD curves of the Ni₂Cr₁-LDN, Ni₃Cr₁-LDN, Ni₁Cr₁-LDN, Ni₁Cr₂-LDN, and Ni₂Cr₁-LDH electrodes at 2 A g⁻¹. The LDNs had the highest discharge time when the ratio of Ni²⁺ to Cr³⁺ was 2 : 1. Fig. S8d† shows the GCD curves of the Ni₂Cr₁-LDN electrode at various current densities. The GCD curve had flat discharge and charge platforms, and the charge time was basically the same as the discharge time, which suggests that the electrode had good coulombic efficiency and reaction reversibility.⁴⁰ Fig. 5d presents the calculated specific capacitances of the five electrodes at various discharge current densities. When the current density was set at 2 A g⁻¹, the specific capacitances of the Ni₂Cr₁-LDN, Ni₃Cr₁-LDN, Ni₁Cr₁-LDN, and Ni₁Cr₂-LDN electrodes were 1525, 1027, 651, and 324 F g⁻¹. When the current density was gradually increased to 10 A g⁻¹, their specific capacitances diminished correspondingly to 957, 477, 253, and 183 F g⁻¹, and the capacitance retentions reached up to 62.8%, 46.4%, 41.1%, and 56.5%, respectively. The specific capacitance of Ni₂Cr₁-LDHs only retained 29.0% (347.5 F g⁻¹) at 10 A g⁻¹ versus 1198 F g⁻¹ at

2 A g⁻¹, showing the minimum performance rate among the five samples. This is because the accumulation of layers blocked the flow of ions, while the partial peeling of the laminates after ultrasonication facilitated the rapid flow of ions. When the current density increased and the transfer of ions and charge sped up, the influence of the stacked laminate structure of LDHs became more obvious.

The cyclability of the five electrodes is displayed in Fig. 6a. The capacitance retentions of the Ni₂Cr₁-LDN, Ni₃Cr₁-LDN, Ni₁Cr₁-LDN, Ni₁Cr₂-LDN, and Ni₂Cr₁-LDH electrodes were 86%, 80%, 76%, 93%, and 59% after 1000 cycles, suggesting that the LDNs exfoliated by ultrasound had a higher cycling stability. EIS was introduced to study the resistance of the NiCr-LDN electrodes (Fig. 6b). The diameter of the semicircle in the high-frequency range reflects the charge transfer resistance (R_{ct}). The R_{ct} values of Ni₂Cr₁-LDNs, Ni₃Cr₁-LDNs, Ni₁Cr₁-LDNs, Ni₁Cr₂-LDNs and Ni₂Cr₁-LDHs were 0.26, 0.50, 0.64, 1.32, and 1.57 Ω , respectively, and the charge transfer resistance of Ni₂Cr₁-LDNs was the lowest. A low R_{ct} was important for enhancing the electrical conductivity and excellent rate capability. This result was associated with the reduced thickness of the layers and the increased specific surface area, which could facilitate the diffusion of electrolyte ions and fast kinetics. As listed in Table 1, the electrochemical performance of Ni₂Cr₁-LDNs was comparable with or superior to that of LDH-based materials in the literature. Therefore, this material is a promising electrode material for high-performance supercapacitors.

In general, the main reasons for the remarkable performance of the Ni₂Cr₁-LDNs could be attributed to the following features: first, the process of ultrasonication during co-precipitation resulted in the exfoliation of LDHs and the formation of nanoflakes.⁵ LDH nanoflakes had more active sites than the stacked LDHs, which facilitated rapid ion transport, leading to more efficient charging/discharging.^{25,26} Second, the Cr³⁺ ion had a special electronic configuration ($t_{2g}^3e_g^0$).^{48,49} The introduction of Cr³⁺ into LDNs could promote electron capture and charge transfer.^{48–50} However, the Cr³⁺ ion itself did not take part in the faradaic redox reaction. When more Cr³⁺ ions were dropped into the LDNs, the capacitance performance decreased

Table 1 Comparison of the electrochemical performance of LDH-based materials

Materials	Specific capacitance	Current density	Electrolyte	Ref.
GO/CoAl-LDHs	825 F g ⁻¹	1 A g ⁻¹	6 M NaOH	20
CoAl-LDHs	838 F g ⁻¹	1 A g ⁻¹	6 M KOH	41
NiMn-LDHs/C	1634 F g ⁻¹	1 A g ⁻¹	6 M KOH	42
NiMn-LDHs	1202 F g ⁻¹	5 A g ⁻¹	1 M KOH	12
NiCo-LDHs/GO	1489 F g ⁻¹	1 A g ⁻¹	6 M KOH	43
NiCo ₂ O ₄ @NiFe-LDHs	1160 F g ⁻¹	1 A g ⁻¹	2 M KOH	44
NiO/NiMn-LDHs	937 F g ⁻¹	0.5 A g ⁻¹	3 M KOH	14
NiFe-LDHs	1462.5 F g ⁻¹	5 A g ⁻¹	2 M KOH	15
CoAl-LDHs/rGO	1492 F g ⁻¹	1 A g ⁻¹	6 M KOH	22
NiMn-LDHs	733.8 F g ⁻¹	1 A g ⁻¹	1 M LiOH	45
NiMn-LDHs/Ni foam	1511 F g ⁻¹	2.5 A g ⁻¹	1 M KOH	46
NiCoAl-LDHs	1137 F g ⁻¹	0.5 A g ⁻¹	6 M KOH	7
NiCo-LDHs	1410 F g ⁻¹	2 A g ⁻¹	6 M KOH	47
CoS _x /Ni-Co LDHs	1562 F g ⁻¹	1 A g ⁻¹	2 M KOH	10
Ni ₂ Cr ₁ -LDNs	1525 F g ⁻¹	2 A g ⁻¹	6 M KOH	This work



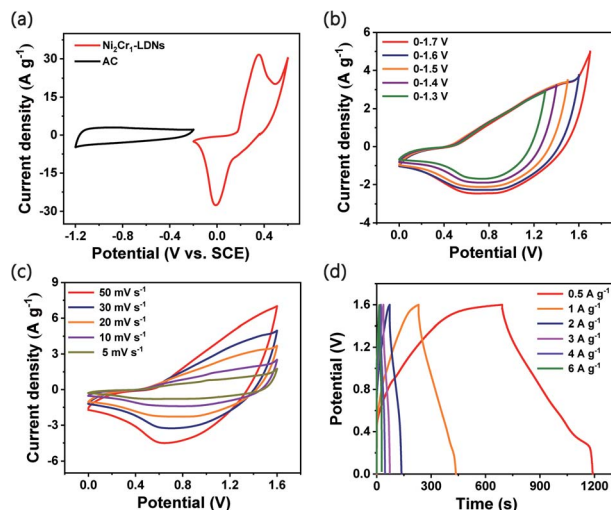


Fig. 7 (a) CV curves of $\text{Ni}_2\text{Cr}_1\text{-LDNs}$ and AC at a scan rate of 10 mV s^{-1} , (b) CV curves of the ASC performed in different potential windows at 20 mV s^{-1} , (c) CV curves at different scan rates from 5 to 50 mV s^{-1} , and (d) GCD curves at different current densities.

instead. Thus, a suitable $\text{Ni}^{2+}/\text{Cr}^{3+}$ ratio ($2 : 1$) was essential for achieving high capacitance.

Electrochemical characterization of the asymmetric supercapacitor

An asymmetric supercapacitor (ASC) device was assembled to demonstrate the practical applications of the $\text{Ni}_2\text{Cr}_1\text{-LDN}$ electrodes. The device was denoted as the $\text{Ni}_2\text{Cr}_1\text{-LDN//AC}$ ASC. The related electrochemical characteristics of the AC electrode in a 6 M KOH electrolyte are shown in Fig. S9.† Fig. 7a exhibits the CV curves of the $\text{Ni}_2\text{Cr}_1\text{-LDN}$ electrode and AC electrode at a scan rate of 10 mV s^{-1} . Fig. 7b shows the CV curves of $\text{Ni}_2\text{Cr}_1\text{-LDN//AC}$ ASC in different voltage windows. Polarization occurred when the operating potential was higher than 1.6 V . Therefore, $0\text{--}1.6 \text{ V}$ was selected as the suitable operating potential window of the $\text{Ni}_2\text{Cr}_1\text{-LDN//AC}$ ASC. Fig. 7c exhibits the CV curves of the $\text{Ni}_2\text{Cr}_1\text{-LDN//AC}$ ASC at scan rates from 5 to 50 mV s^{-1} . They presented strong redox peaks, indicating the pseudocapacitive behaviour of the ASC. Fig. 7d shows the GCD curves of the $\text{Ni}_2\text{Cr}_1\text{-LDN//AC}$ ASC at various current densities with a voltage range from 0 to 1.6 V , which also revealed the pseudocapacitive behaviour. The specific capacitance of the $\text{Ni}_2\text{Cr}_1\text{-LDN//AC}$ ASC reached 155 F g^{-1} at 0.5 A g^{-1} , and 49.5 F g^{-1} was retained at 6 A g^{-1} with a capacitance retention of 31.9% .

Fig. 8a shows the Ragone plots of the $\text{Ni}_2\text{Cr}_1\text{-LDN//AC}$ ASC. The $\text{Ni}_2\text{Cr}_1\text{-LDN//AC}$ ASC presented a maximum energy density of $55.33 \text{ W h kg}^{-1}$ at 400 W kg^{-1} . Besides, the energy density of the $\text{Ni}_2\text{Cr}_1\text{-LDN//AC}$ ASC was maintained at $18.27 \text{ W h kg}^{-1}$, even at a power density of 4800 W kg^{-1} . These values were comparable with or superior to those of most reported ASCs, such as $\text{NiFe LDHs/rGO/NF/MC}$ ($17.71 \text{ W h kg}^{-1}$ at 348.49 W kg^{-1}),¹⁵ NiAl-LDHs/rGO/AC (15.4 W h kg^{-1} at 230 W kg^{-1}),⁵¹ $\text{CC@NiCo}_2\text{Al-LDHs/CC@ZPC}$ (44 W h kg^{-1} at 462 W kg^{-1}),⁷ CoMn-LDHs/AC (4.4 W h kg^{-1} at 2500 W kg^{-1}),⁵² NiCo-LDHs/

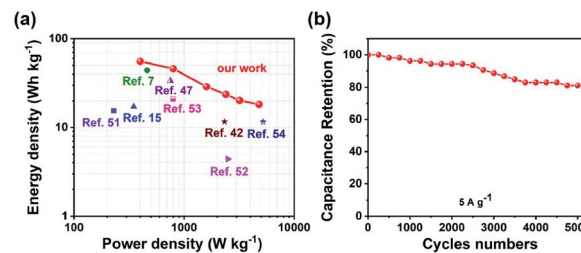


Fig. 8 (a) Ragone plot related to the energy and power density of the ASC, (b) cycling performance of the ASC.

graphene/nickel foam//AC ($33.75 \text{ W h kg}^{-1}$ at 750 W kg^{-1}),⁴⁷ NiMn-LDHs/PC//AC ($11.65 \text{ W h kg}^{-1}$ at $2330.16 \text{ W kg}^{-1}$),⁴² NiAl-LDHs/AC (21 W h kg^{-1} at 800 W kg^{-1}),⁵³ and $\text{NiCo}_2\text{O}_4\text{//AC}$ (11.6 W h kg^{-1} at 5220 W kg^{-1}),⁵⁴ shown in Fig. 8a. Moreover, the $\text{Ni}_2\text{Cr}_1\text{-LDN//AC}$ ASC exhibited good cycling stability (Fig. 8b), with 81.1% of the capacitance retained, even after 5000 cycles.

Conclusions

We have successfully synthesized thin NiCr-LDN nanoflakes for a supercapacitor with various $\text{Ni}^{2+}/\text{Cr}^{3+}$ ratios in one-step, efficient synthesis without hydrothermal treatment or extra exfoliation using organic solvents. These as-prepared LDH nanoflakes, with a $4\text{--}5 \text{ nm}$ thickness, displayed increased contact area and enhanced capacitance and facilitated the diffusion of ions. The optimal $\text{Ni}_2\text{Cr}_1\text{-LDN}$ (4.7 nm thickness) nanoflakes displayed an excellent specific capacitance of 1525 F g^{-1} at a current density of 2 A g^{-1} , and a low charge transfer resistance of 0.26Ω . Besides, the assembled $\text{Ni}_2\text{Cr}_1\text{-LDN//AC}$ ASC delivered an outstanding energy density of $55.22 \text{ W h kg}^{-1}$ at a power density of 400 W kg^{-1} and retained 81.1% of the original specific capacitance, even after 5000 cycles. This work provides a facile approach to efficiently synthesize LDH nanoflakes for energy storage.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors acknowledged the financial supports from Key-Area Research and Development Program of Guangdong Province (2019B110209003), Guangdong Basic and Applied Basic Research Foundation (2019B1515120058, 2020A1515011149), National Key R&D Program of China (2018YFD0800700), National Ten Thousand Talent Plan, National Natural Science Foundation of China (21776324), the Fundamental Research Funds for the Central Universities (19lgzd25), and Hundred Talent Plan (201602) from Sun Yat-sen University.

References

- 1 Q. Wang and D. O'Hare, *Chem. Rev.*, 2012, **112**, 4124–4155.



- 2 P. J. Sideris, U. G. Nielsen, Z. Gan and C. P. Grey, *Science*, 2008, **321**, 113–117.
- 3 G. L. Fan, F. Li, D. G. Evans and X. Duan, *Chem. Soc. Rev.*, 2014, **43**, 7040–7066.
- 4 J. Feng, Y. He, Y. Liu, Y. Du and D. Li, *Chem. Soc. Rev.*, 2015, **44**, 5291–5319.
- 5 R. Li, Y. Liu, H. Li, M. Zhang, Y. Lu, L. Zhang, J. Xiao, F. Boehm and K. Yan, *Small Methods*, 2019, **3**, 1800344.
- 6 K. Yan, T. Lafleur, J. Chai and C. Jarvis, *Electrochem. Commun.*, 2016, **62**, 24–28.
- 7 X. Gao, X. Liu, D. Wu, B. Qian, Z. Kou, Z. Pan, Y. Pang, L. Miao and J. Wang, *Adv. Funct. Mater.*, 2019, **29**, 1903879.
- 8 Y. Liu, M. Zhang, D. Hu, R. Li, K. Hu and K. Yan, *ACS Appl. Energy Mater.*, 2019, **2**, 1162–1168.
- 9 H. Chen, L. Hu, M. Chen, Y. Yan and L. Wu, *Adv. Funct. Mater.*, 2014, **24**, 934–942.
- 10 X. Guan, M. Huang, L. Yang, G. Wang and X. Guan, *Chem. Eng. J.*, 2019, **372**, 151–162.
- 11 M. Zhang, Y. He, D. Yan, H. Xu, A. Wang, Z. Chen, S. Wang, H. Luo and K. Yan, *Nanoscale*, 2019, **11**, 22255–22260.
- 12 X. Wang, J. Zhang, S. Yang, H. Yan, X. Hong, W. Dong, Y. Liu, B. Zhang and Z. Wen, *Electrochim. Acta*, 2019, **295**, 1–6.
- 13 W. Wang, N. Zhang, Z. Shi, Z. Ye, Q. Gao, M. Zhi and Z. Hong, *Chem. Eng. J.*, 2018, **338**, 55–61.
- 14 P. F. Liu, J. J. Zhou, G. C. Li, M. K. Wu, K. Tao, F. Y. Yi, W. N. Zhao and L. Han, *Dalton Trans.*, 2017, **46**, 7388–7391.
- 15 M. Li, R. Jijie, A. Barras, P. Roussel, S. Szunerits and R. Boukherroub, *Electrochim. Acta*, 2019, **302**, 1–9.
- 16 H. Zhang, M. Usman Tahir, X. Yan, X. Liu, X. Su and L. Zhang, *Chem. Eng. J.*, 2019, **368**, 905–913.
- 17 M. Zhang, Y. Liu, B. Liu, Z. Chen, H. Xu and K. Yan, *ACS Catal.*, 2020, **10**, 5179–5189.
- 18 P. Yuan, N. Zhang, D. Zhang, T. Liu, L. Chen, X. Liu, R. Ma and G. Qiu, *Chem. Commun.*, 2014, **50**, 11188–11191.
- 19 F. Song and X. Hu, *Nat. Commun.*, 2014, **5**, 4477.
- 20 Y. Zhong, Y. Liao, A. Gao, J. Hao, D. Shu, Y. Huang, J. Zhong, C. He and R. Zeng, *J. Alloys Compd.*, 2016, **669**, 146–155.
- 21 Q. Du, L. Su, L. Hou, G. Sun, M. Feng, X. Yin, Z. Ma, G. Shao and W. Gao, *J. Alloys Compd.*, 2018, **740**, 1051–1059.
- 22 J. Li, P. Zhang, X. Zhao, L. Chen, J. Shen, M. Li, B. Ji, L. Song, Y. Wu and D. Liu, *J. Colloid Interface Sci.*, 2019, **549**, 236–245.
- 23 Y. Wang, C. Xie, Z. Zhang, D. Liu, R. Chen and S. Wang, *Adv. Funct. Mater.*, 2018, **28**, 1703363.
- 24 Z. Yi, C. Ye, M. Zhang, Y. Lu, Y. Liu, L. Zhang and K. Yan, *Appl. Surf. Sci.*, 2019, **480**, 256–261.
- 25 D. Chen, S. Yan, H. Chen, L. Yao, W. Wei, H. Lin and S. Han, *Electrochim. Acta*, 2018, **292**, 374–382.
- 26 A. D. Jagadale, G. Guan, X. Li, X. Du, X. Ma, X. Hao and A. Abudula, *Chem. Eng. J.*, 2018, **336**, 562–569.
- 27 D. P. Debecker, E. M. Gaigneaux and G. Busca, *Chem.–Eur. J.*, 2009, **15**, 3920–3935.
- 28 B. M. Hunter, W. Hieringer, J. R. Winkler, H. B. Gray and A. M. Müller, *Energy Environ. Sci.*, 2016, **9**(5), 1734–1743.
- 29 X. Y. Liu, Y. Q. Gao and G. W. Yang, *Nanoscale*, 2016, **8**(7), 4227–4235.
- 30 Y. Tao, L. Zaijun, L. Ruiyi, N. Qi, K. Hui, N. Yulian and L. Junkang, *J. Mater. Chem.*, 2012, **22**, 23587–23592.
- 31 Z. Cai, D. Zhou, M. Wang, S. Bak, Y. Wu, Z. Wu, Y. Tian, X. Xiong, Y. Li, W. Liu, S. Siahrostami, Y. Kuang, X. Q. Yang, H. Duan, Z. Feng, H. Wang and X. Sun, *Angew. Chem., Int. Ed.*, 2018, **57**, 9392–9396.
- 32 H. Ali-Löytty, M. W. Louie, M. R. Singh, L. Li, H. G. Sanchez Casalongue, H. Ogasawara, E. J. Crumlin, Z. Liu, A. T. Bell, A. Nilsson and D. Friebe, *J. Phys. Chem. C*, 2016, **120**, 2247–2253.
- 33 M. C. Biesinger, B. P. Payne, A. Grosvenor, L. W. M. Lau, A. Gerson and R. S. C. Smart, *Appl. Surf. Sci.*, 2011, **257**, 2717–2730.
- 34 M. C. Biesinger, B. P. Payne, L. W. M. Lau, A. Gerson and R. S. C. Smart, *Surf. Interface Anal.*, 2009, **41**, 324–332.
- 35 S. Chen, Y. Huang, X. Han, Z. Wu, C. Lai, J. Wang, Q. Deng, Z. Zeng and S. Deng, *Chem. Eng. J.*, 2018, **352**, 306–315.
- 36 Y. Guo, X. Hong, Y. Wang, Q. Li, J. Meng, R. Dai, X. Liu, L. He and L. Mai, *Adv. Funct. Mater.*, 2019, **29**, 1809004.
- 37 A. L. Yan, X. C. Wang and J. P. Cheng, *Nanomaterials*, 2018, **8**, 747.
- 38 W. Ma, R. Ma, J. Wu, P. Sun, X. Liu, K. Zhou and T. Sasaki, *Nanoscale*, 2016, **8**, 10425–10432.
- 39 E. Laviron, *J. Electroanal. Chem. Interfacial Electrochem.*, 1979, **101**, 19–28.
- 40 Y. Tao, L. Ruiyi, Z. Lin, M. Chenyang and L. Zaijun, *Electrochim. Acta*, 2015, **176**, 1153–1164.
- 41 J. Zai, Y. Liu, X. Li, Z. F. Ma, R. Qi and X. Qian, *Nano-Micro Lett.*, 2017, **9**, 21.
- 42 M. Yu, R. Liu, J. Liu, S. Li and Y. Ma, *Small*, 2017, **13**, 1702616.
- 43 J. Yang, C. Yu, C. Hu, M. Wang, S. Li, H. Huang, K. Bustillo, X. Han, C. Zhao, W. Guo, Z. Zeng, H. Zheng and J. Qiu, *Adv. Funct. Mater.*, 2018, **28**, 1803272.
- 44 G. Luo, K. S. Teh, Y. Xia, Z. Li, Y. Luo, L. Zhao and Z. Jiang, *J. Alloys Compd.*, 2018, **767**, 1126–1132.
- 45 X. L. Guo, J. M. Zhang, W. N. Xu, C. G. Hu, L. Sun and Y. X. Zhang, *J. Mater. Chem. A*, 2017, **5**, 20579–20587.
- 46 X. L. Guo, X. Y. Liu, X. D. Hao, S. J. Zhu, F. Dong, Z. Q. Wen and Y. X. Zhang, *Electrochim. Acta*, 2016, **194**, 179–186.
- 47 Y. Bai, W. Wang, R. Wang, J. Sun and L. Gao, *J. Mater. Chem. A*, 2015, **3**, 12530–12538.
- 48 K. Yan, Y. Liu, Y. Lu, J. Chai and L. Sun, *Catal. Sci. Technol.*, 2017, **7**, 1622–1645.
- 49 K. Yan and A. Chen, *Energy*, 2013, **58**, 357–363.
- 50 Y. Yang, L. Dang, M. J. Shearer, H. Sheng, W. Li, J. Chen, P. Xiao, Y. Zhang, R. J. Hamers and S. Jin, *Adv. Energy Mater.*, 2018, **8**, 1703189.
- 51 X. Ge, C. Gu, Z. Yin, X. Wang, J. Tu and J. Li, *Nano Energy*, 2016, **20**, 185–193.
- 52 A. D. Jagadale, G. Guan, X. Li, X. Du, X. Ma, X. Hao and A. Abudula, *J. Power Sources*, 2016, **306**, 526–534.
- 53 L. Zhang, H. Yao, Z. Li, P. Sun, F. Liu, C. Dong, J. Wang, Z. Li, M. Wu, C. Zhang and B. Zhao, *J. Alloys Compd.*, 2017, **711**, 31–41.
- 54 X. Li, L. Jiang, C. Zhou, J. Liu and H. Zeng, *NPG Asia Mater.*, 2015, **7**, e165.

