

## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)

Cite this: *Green Chem.*, 2021, **23**, 8940

## Uncovering the potential of aqueous solutions of deep eutectic solvents on the extraction and purification of collagen type I from Atlantic codfish (*Gadus morhua*)†

Meena Bisht,<sup>a</sup> Margarida Martins,<sup>a</sup> Ana C. R. V. Dias,<sup>b</sup> Sónia P. M. Ventura<sup>a</sup> and João A. P. Coutinho<sup>a</sup>

Marine fish industries discard huge amounts of fish waste every year, which in turn impose problems of environmental pollution and loss of economic value. About 75% of the total weight of fish is discarded in the form of skins, bones, fins, heads, guts, and scales, which contain high levels of collagen type I. Generally, major sources for commercial collagens are the skin and bone of pigs and cows; however, these sources are chiefly associated with the risk of transference of zoonotic diseases or religious issues. Traditional protocols applied to the extraction of collagen are outdated, mainly with respect to present demands to develop more sustainable processes. This work explores the use of sustainable solvents, such as deep eutectic solvents (DES), to develop a more efficient, cost-effective and biocompatible process to extract collagen from waste from the fish industry waste. The extraction of collagen from the skin of Atlantic cod (*Gadus morhua*) using aqueous solutions of various eutectic solvents was studied, and after selection of the best solvent, an aqueous solution of urea (U) and lactic acid (LA) at a molar ratio of 1 : 2 (U : LA 1 : 2), the collagen extracted was properly characterized using SDS-PAGE, CD, FTIR, and XRD, and shown to be of type I. The results obtained here demonstrate an improvement in the yield and quality of the extracted collagen when eutectic mixtures were applied instead of acetic acid. After optimization of the process conditions, a maximum extraction yield of 6% was obtained for the aqueous solution of U : LA 1 : 2 at 0.75 M. The present work demonstrates the potential use of codfish skin waste and an aqueous solution of a DES to develop a more environmentally-friendly process to obtain high-quality collagen type I. It is an effort to convince industries to valorize their own residues under the guidelines of a circular economy.

Received 24th April 2021,  
Accepted 30th September 2021

DOI: 10.1039/d1gc01432c

[rsc.li/greenchem](http://rsc.li/greenchem)

## Introduction

A million metric tonnes of waste are discarded every year from fish processing activities, making fish processing waste management a major challenge worldwide.<sup>1</sup> In this field, approximately 70% of wastes in the form of skin, bones, fins, heads and scales are produced, which could be used as natural sources of several bioactive compounds. Collagen is one of the most abundant compounds present in these fish wastes.<sup>2</sup> It is a fibrous protein constituting a major structural element in the connective tissue of animal skin and bone.<sup>2,3</sup> It consists of three polypeptide

chains that fold into a unique triple helix structure, resulting in a repeating glycine-(2*S*)-proline-(2*S*,4*R*)-4-hydroxyproline (Gly-Xaa-Yaa) sequence, in which every third residue is Gly.<sup>4</sup> To date, 29 types of collagen have been identified. The global collagen market is expected to grow at an annual growth rate of 5.9% to reach USD 6.63 billion in the near future by 2025.<sup>5</sup> Collagen has a wide range of applications in the food, pharmaceutical, healthcare, tissue engineering, cosmetics and biotechnological industries, as depicted in detail in Fig. S1.†<sup>6–8</sup>

Europe has dominated the collagen market with a share of 35.1% in 2019, which is attributed to multiple nutritional, skin, and health benefits of collagen and growing *per capita* healthcare spending in the region. In the specific case of collagen type I, the type most abundantly found in fish-derived materials, the principal applications are those related to the biomedical sector.<sup>5–7</sup> Generally, major sources of commercial collagens are the skin and bone of pigs and cows (see Fig. S1†). However, these sources are chiefly associated with the risk of transference of zoonotic diseases or religious issues.<sup>8,9</sup> Thus, there is a strong need to

<sup>a</sup>CICECO – Aveiro Institute of Materials, Department of Chemistry, University of Aveiro, 3810-193 Aveiro, Portugal. E-mail: [meenabisht56@gmail.com](mailto:meenabisht56@gmail.com), [spventura@ua.pt](mailto:spventura@ua.pt)

<sup>b</sup>CESAM – Centre for Environmental and Marine Studies, Department of Environment and Planning, University of Aveiro, 3810-193 Aveiro, Portugal

†Electronic supplementary information (ESI) available: Detailed data for the phase diagrams are presented. See DOI: 10.1039/d1gc01432c

search for alternative sources of collagen, for which collagen from fish can be considered the best alternative.<sup>8,10</sup> Codfish is thus a good example to consider. It is consumed daily in large quantities and in several countries, among which Portugal stands out. As a result, huge amounts of skin, scales, and bone residues are generated, in which the presence of collagen type I is significant. In recent years, collagen from Baltic cod (*Gadus morhua*), silvertip shark (*Carcharhinus albimarginatus*), deep-sea redfish (*Sebastes mentella*), striped catfish (*Pangasianodon hypophthalmus*), carp (*Catla catla* and *Cirrhinus mrigala*) and of Nile tilapia (*Oreochromis niloticus*) has been extracted and characterized.<sup>11–13</sup> In the literature, the most common processes represent the use of acidic treatments or enzymatic hydrolysis. In spite of their capacity to recover collagen, there are some drawbacks, such as the complexity of some processes and the harsh operational conditions used<sup>13–16</sup> that need further attention. As an example, the extraction of collagen performed by acids occurs traditionally at high temperatures, which does not help preserve its structural integrity, consequently inhibiting the capacity of the process to control the degradation rate.<sup>17</sup> In recent years, deep eutectic solvents (DES) and eutectic mixtures have been reported for the dissolution and extraction of many bioactive compounds.<sup>18–25</sup> DES are composed of at least a hydrogen bond acceptor (HBA) and a hydrogen bond donor (HBD) species, which upon mixing establish strong hydrogen bond interactions leading to the formation of eutectic mixtures, often becoming liquid at conditions close to room temperature.<sup>21</sup> The use of eutectic mixtures, by the addition of water to DES for extraction purposes is a well-established procedure.<sup>22,23</sup> It helps reduce the solvents' viscosity, thus facilitating the mass transfer process. Moreover, the aqueous solutions exhibited higher dissolving rates and lower cost compared to neat DES.<sup>24</sup> Indeed, after the work done by Triolo and co-workers<sup>26</sup> and already adopted and accepted by other authors, water may be a component of the DES, being able to act as an HBD or an HBA. It is probably true that the hydrogen bonding network between the starting materials present in the neat DES is destroyed up to specific amounts of water, but a new hydrogen bonding network would be formed in which water participates with a positive impact on developing extraction processes. Therefore, the use of aqueous solutions of DES extracting collagen type I represents here a poorly explored but highly promising strategy<sup>25</sup> to reduce the adverse environmental effects of the overall process, but mainly to improve the yield of extraction and purity level of the collagen. Nevertheless, and although the work of Bai *et al.*<sup>25</sup> reports the use of DES to process a similar raw material – codfish skins – their objective is different, since they were focused on the extraction and purification of collagen peptides (a product of the thermal degradation of collagen). Furthermore, we also intend to use the DES as a way to have better control over the temperature of extraction (low temperatures will be preferred), to avoid the thermal degradation of collagen.<sup>17</sup>


Collagen type I was extracted from codfish skin waste using 0.5 M of acetic acid as the control solvent, with these results compared with those obtained with aqueous solutions of DES. DES containing betaine (Bet), urea (U), and cholinium chloride

(CC) as hydrogen bond acceptors (HBA) and formic acid (FA), acetic acid (AA), propanoic acid (PA), and lactic acid (LA) as hydrogen bond donors (HBD) were applied (Fig. 1). The solid–liquid ratio, pH, and concentration of DES were the conditions investigated and further optimized. The molar ratio of DES used was 1 : 2, except for the cases of U : FA (1 : 4) and U : AA (1 : 5). The extracted collagen was characterized using Fourier Transform Infrared Spectroscopy (FTIR), Sodium Dodecyl Sulfate-Polyacrylamide Gel Electrophoresis (SDS-PAGE), X-Ray Diffraction (XRD), Circular Dichroism (CD), and Differential Scanning Calorimetric (DSC) studies and the process was developed by considering the best DES analysed regarding its life cycle assessment (LCA). The total impacts evaluated relating to the environmental categories of global warming, ozone formation, human health, terrestrial acidification, mineral and fossil resources scarcity were the issues determined.

## Materials and methods

### Materials

Commercial rat tail collagen was purchased from Sigma-Aldrich. Formic acid (98%) and urea (>99%) were purchased from Panreac, acetic acid (99%) was supplied by Fisher Scientific, propionic acid (>99%) was acquired from Merck Chemicals, L(+)-lactic acid (88–92%) from Riedel de Haën, *p*-toluenesulfonic acid monohydrate (>98.5%) from Sigma-Aldrich, and cholinium chloride (99%) and betaine (98%) were purchased from Acros Organics. The water content of all starting materials used in DES preparation was measured using a Metrohm 831 Karl Fisher coulometer. Sodium chloride (99.5%) was purchased from Panreac. Isopropanol (HPLC Grade) was obtained from Fisher Chemical. Sodium acetate (100%) was purchased from VWR – Prolabo (JMS). The skins of Baltic cod (*Gadus morhua*) were kindly supplied by Pascoal & Filhos S.A. (Aveiro, Portugal) and stored frozen at a temperature of –20 °C until use.

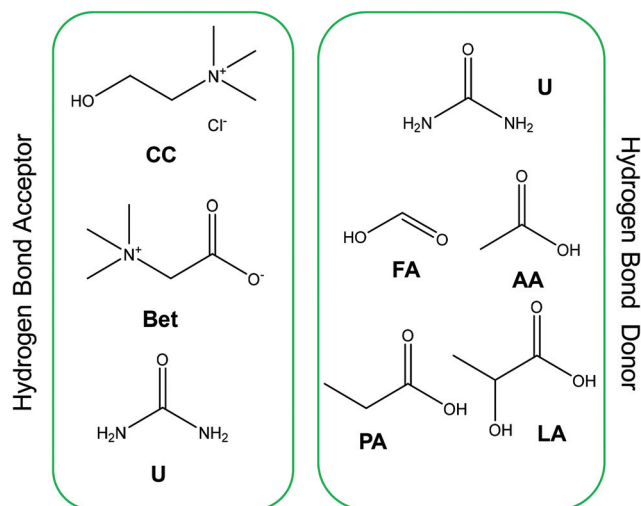

**Fig. 1** Chemical structures of HBDs and HBAs used to prepare the DES under study in this work.

## Experimental methods

### DES preparation

DES were prepared using a method adapted from Abbot and co-workers.<sup>20</sup> Firstly, the amount of water present in the starting materials was measured using a Metrohm 831 Karl Fisher coulometer (Table S1 from ESI†). Then, two-component mixtures (HBD and HBA) were accurately weighed into a round-bottom flask. The mixtures were stirred in an oil bath at  $60 \pm 2$  °C at 500 rpm until a homogenous and transparent liquid was obtained. The pH of all aqueous solutions was measured at room temperature using a Mettler Toledo S47 SevenMulti™ dual meter pH and conductivity equipment with an uncertainty of  $\pm 0.01$ .

### Extraction of collagen from codfish skin

All procedures were carried out at 4 °C. Collagen was extracted according to the previously reported method with slight modifications.<sup>27,28</sup> A detailed schematic representation of the extraction and recovery process for collagen from codfish skin waste using aqueous solutions of acetic acid (control solvent) and DES is shown in Fig. S2 in ESI.† Briefly, the frozen codfish skins collected from Pascoal & Filhos S.A. were thawed, and the attached meat, scales and fins were manually removed. The superfluous material from the fish skins was removed by cleaning and rinsing with cold water. Then, the skins were cut into small pieces. Non-collagenous proteins were removed by soaking the skins with 0.1 M sodium hydroxide (NaOH) solution with a solid to solvent ratio of 1 : 10 (w/v) for 24 h, where the NaOH solution was changed after every 5–6 h. After that, the samples were washed with cold distilled water until a neutral pH was obtained. The deproteinized skins were defatted using a 10% (v/v) butyl alcohol solution with a solid to solvent ratio of 1 : 10 (w/v) for 48 h and the solvent was changed after every 6–7 h. Again, the samples were washed with cold distilled water. Then, the extractions were performed at 4 °C for 48 h using an optimized solid–liquid ratio of 1 : 10 (w/v) in 0.5 M of acetic acid or aqueous solutions of DES and using an orbital shaker. The resultant viscous solution was centrifuged to remove insoluble substances. The supernatants were salted-out by adding NaCl to a final concentration of 0.9 M, followed by precipitation of the collagen by the addition of NaCl (final concentration of 2.6 M) at neutral pH (0.05 M Tris-HCl, pH 7.5). The resultant precipitate was obtained by centrifugation at 15 000g for 1 h and dialyzed against deionized water at 4 °C for 72 h. Finally, the collagen was dried by lyophilization, and its yield was calculated using eqn (1):<sup>29</sup>

$$\text{Yield (\%)} = \frac{\text{weight of dried collagen (g)}}{\text{weight of dried skins (g)}} \times 100 \quad (1)$$

### Fourier-transform infrared spectroscopy (FTIR)

The presence of collagen type I in the samples was determined by an FTIR spectrometer (Bruker Tensor 27) equipped with a single horizontal Golden Gate ATR cell (attenuated total reflection), and a diamond crystal. FTIR spectra were collected in

the range of 4000–250  $\text{cm}^{-1}$  by accumulating 256 scans, and with a resolution of 4  $\text{cm}^{-1}$ . After measuring all FTIR spectra corresponding to a selected strain and background subtraction, the average spectra were calculated.

### Sodium dodecyl sulfate-polyacrylamide gel electrophoresis (SDS-PAGE)

An electrophoresis analysis was performed on polyacrylamide gels (stacking: 4% and resolving: 20%) with a running buffer (pH 8.3) consisting of 250 mM of Tris-HCl, 1.92 M of glycine, and 1% SDS. The collagen samples were stained with the usual staining procedure [Coomassie Brilliant Blue G-250 0.1% (w/v), methanol 50% (v/v), acetic acid 7% (v/v), and water 42.9% (v/v)] in an orbital shaker, at moderate speed ( $\pm 50$  rpm), for 4 h and at room temperature. The gels were stained in a solution containing acetic acid 7% (v/v), methanol 20% (v/v), and water 73% (v/v) in an orbital shaker at  $\pm 60$  rpm overnight, also at room temperature. SDS-PAGE Molecular Weight Standards (VWR) were used as protein standards.

### Circular dichroism (CD)

CD spectra of the extracts were recorded at 180 to 280 nm using a 0.1 cm path length cuvette. Lyophilised collagen samples were dissolved at 0.5  $\text{mg mL}^{-1}$  in 1% AA and incubated at 4 °C for 6 h. The baseline of the sample CD spectrum was corrected by subtracting the CD spectrum of the solvent alone. Each CD spectrum represents an average of three scans. The bandwidth and response time were, respectively, 1.0 nm and 1 s. For thermal melting ( $T_m$ ) measurement, a cell holder with quartz cells containing collagen solutions was heated from 2 to 30 °C at a heating rate of 0.1 °C  $\text{min}^{-1}$  at 222 nm.

### Differential scanning calorimetry (DSC)

The thermal stability of the collagen was assessed on a nano-DSC (TA Instruments, New Castle, DE, USA). The collagen sample was degassed for 5 min at 25 °C prior to the scans. All thermograms were recorded from 0 to 35 °C at a constant heating rate of 0.25 °C  $\text{min}^{-1}$  and 600 s of equilibration time. During heating, cells were pressurized to 3 atmospheres. The denaturation temperature of the collagen samples was analyzed using DSC Nanoanalyze software.

### X-Ray diffraction (XRD)

X-Ray Diffraction (XRD) patterns were recorded at room temperature on an Empyrean, Malvern Panalytical powder diffractometer system using  $\text{CuK}\alpha$  radiation (45 kV, 40 mA,  $\text{CuK}\alpha$  radiation of  $\lambda = 1.54018$  Å with  $2\theta$  range from 5° to 50° at a scan speed of 0.0263° per seconds<sup>1</sup>).

### Environmental assessment

Life cycle assessment (LCA) was applied to determine the environmental impacts of the experimental methods, including the steps of codfish skin preparation, solubilization, extraction and purification of collagen. Three alternatives for collagen extraction were analysed: with AA (conventional solvent), and with the DESs selected as the best solvents, U : LA (1 : 2)

and U:PA (1:2). The data on the inputs of each system are presented in Table S2† and the impacts of producing those inputs were taken from the ecoinvent database version 3.7.1.<sup>30</sup> ReCiPe 2016 was the impact assessment method selected.<sup>31</sup>

## Results and discussion

### Selection of the most appropriate aqueous solution of DES to extract collagen

Extraction of collagen using 0.5 M of DES or acetic acid (control solvent) was done according to the method of Nagai

*et al.*<sup>27</sup> Fig. 2 shows the yield of extraction of collagen obtained with 0.5 M of acetic acid and various aqueous solutions of DES as solvents. The results show the lowest yield of extraction for CC:U (1:2), which may be explained by the high pH value (pH 7) of this DES, which is far from the acidic media required for collagen extraction. Therefore, we have prepared DESs using three different types of HBA (CC, Bet, and U) and acid HBD (FA, AA, PA, and LA) at various molar ratios, whose pH values are given in Table S3 from ESI.† Among the studied DESs (Fig. 2), CC-based DESs were found to be the least effective at extracting collagen.

Nevertheless, a remarkable improvement in the yield of extraction was recorded when collagen type I was recovered using U-based DES, particularly in the case of Bet:AA (1:2), Bet:PA (1:2), U:PA (1:2), and U:LA (1:2). The yields of extraction of collagen with Bet:AA (1:2), Bet:PA (1:2), U:PA (1:2), and U:LA (1:2) were, respectively, 4.3%, 4.4%, 5.0%, and 5.2% on the basis of lyophilized dry weight. Furthermore, the extraction efficiency of the individual starting materials was compared with the data obtained for the eutectic mixtures, U:LA (Fig. S3†). From the results, we conclude that the individual aqueous solutions, namely LA and U, are not that effective at extracting collagen type I compared to the eutectic mixtures selected as the best solvents.

### Fourier transform infrared spectroscopy (FTIR)

The structural integrity of collagen was characterized by FTIR. The FTIR spectra of the collagen type I from rat tail (commercial collagen), and codfish collagen extracted using AA and the aqueous solutions of DES are shown in Fig. 3. Although the FTIR spectra of commercial collagen show high similarity with the FTIR of collagen extracted using DES, the same behaviour is not verified when the FTIR of both treated and untreated

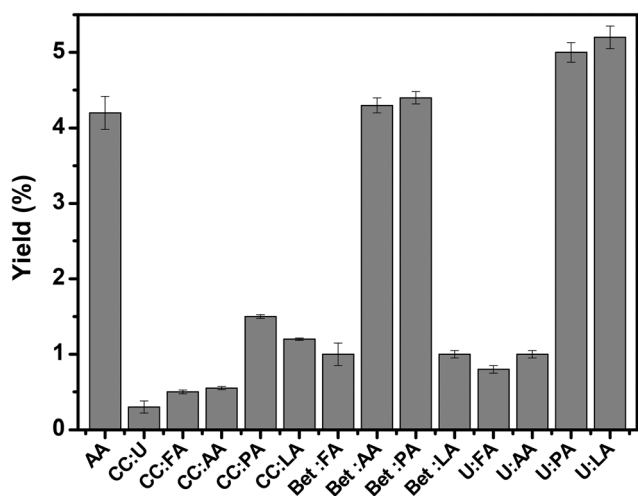


Fig. 2 Yield of extraction of collagen type I (%) and pH obtained by applying several aqueous solutions of DES in comparison with acetic acid (AA) at 0.5 M. All the extractions were done at 4 °C.

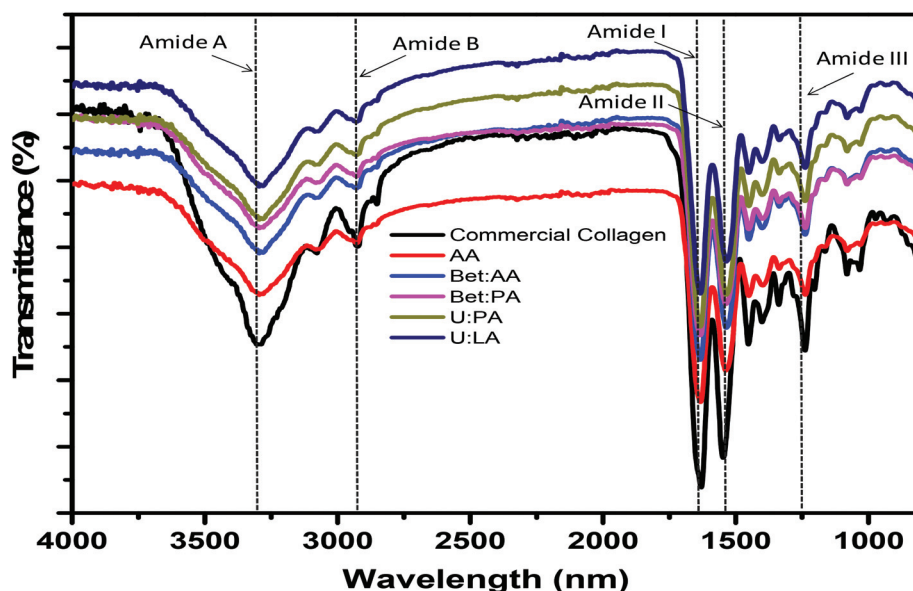


Fig. 3 FTIR spectra of commercial collagen and collagen type I extracted using aqueous solutions of AA and DES. FTIR spectra were collected in the range of 4000–250  $\text{cm}^{-1}$  by accumulating 256 scans, and with a resolution of 4  $\text{cm}^{-1}$  at room temperature.



collagen samples are compared (Fig. S4†). The collagen extracted using DES shows the main absorption bands for amide A at  $3288\text{ cm}^{-1}$ , amide B at  $2926\text{ cm}^{-1}$ , amide I at  $1633\text{ cm}^{-1}$ , amide II at  $1535\text{ cm}^{-1}$ , and amide III at  $1240\text{ cm}^{-1}$ , which are quite similar to the data previously reported for commercial collagen type I.<sup>29–33</sup> The amide A band is associated with N–H stretching vibration. A free N–H stretching vibration occurs in the range of  $3400\text{--}3440\text{ cm}^{-1}$ , and when the NH group of a peptide is involved in a hydrogen bond, the position is shifted to a lower frequency, usually close to  $3300\text{ cm}^{-1}$ .<sup>34–37</sup> Amide B represents the asymmetrical stretch of  $\text{CH}_2$ , while amide I arises from  $\text{C}=\text{O}$  stretching, the amide II band is related to N–H bending vibrations, and the amide III band represents C–H stretching.<sup>31–36</sup> The amide I band is associated with the secondary structure of the protein, and the amide III band confirmed the existence of a helical structure. The absorption ratio between the amide III and  $1450\text{ cm}^{-1}$  bands was close to 1 for the control solvent, and for Bet:PA (1:2), U:LA (1:2) (Table S4 in ESI†), indicating the existence of a triple helix in the collagen extracted from codfish skin,<sup>28,29</sup> since these findings are similar for codfish and other marine species.<sup>29,38–40</sup> The similarities between commercial collagen and collagen extracted from codfish skin confirmed maintenance of the secondary and triple helical structures of collagen type I with aqueous solutions of DES.

#### Sodium dodecyl sulfate polyacrylamide gel electrophoresis (SDS-PAGE)

After proving the structural integrity of collagen type I extracted, its purity was checked by SDS-PAGE. Fig. 4 shows SDS-PAGE patterns of commercial collagen and collagen extracted using aqueous solutions of DES. As reported in the literature, most fish collagens consist of two different  $\alpha$ -chains ( $\alpha 1$  and  $\alpha 2$ ) and a  $\beta$ -chain, characteristic of collagen type I.<sup>41,42</sup>

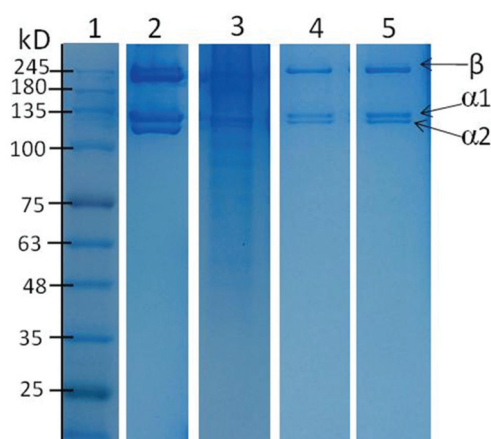


Fig. 4 SDS-PAGE of collagen extracted using various solvents. (1) molecular weight standards; (2) commercial collagen type I from rat tail; (3) collagen type I extracted using an aqueous solution of acetic acid (control solvent); (4) collagen type I extracted using an aqueous solution of Bet:PA (1:2); (5) collagen type I extracted using an aqueous solution of U:LA (1:2) at room temperature.

In Fig. 4, a clear resemblance of the component pattern and molecular weight can be observed for commercial as well as for collagen type I extracted using aqueous solutions of DES.

In this analysis, two  $\alpha$ -chains and one  $\beta$ -chain can be observed, which confirm the collagen extracted as being of type I. Some weak bands below 100 kDa were also observed when acetic acid was used as solvent, whereas no such bands were observed when the aqueous solutions of Bet:PA (1:2) and U:LA (1:2) were applied. These lower bands represent products of degradation of collagen type I promoted during the extraction process.<sup>43</sup> These results show the advantages of using aqueous solutions of DES as solvents instead of the conventional aqueous solution of acetic acid given the high extraction yields and purity achieved while maintaining the structural stability of collagen type I. Taking into account the whole set of results (extraction yields, chemical stability, and purity), the aqueous solution of U:LA at 1:2 was selected as the best solvent to extract collagen type I from codfish skin waste.

#### Circular dichroism (CD) of collagen type I extracted using U:LA (1:2)

CD spectroscopy is typically used to assess the secondary structure of a protein. Therefore, the potential changes in the secondary structure of collagen type I extracted using U:LA (1:2) were further investigated by CD analysis. In the far UV region, the CD spectrum of collagen type I shows a positive maximum at  $220\text{--}222\text{ nm}$ , representative of a triple helix, and a pronounced negative minimum at  $196\text{--}200\text{ nm}$  defining the random coil structure.<sup>23,38</sup> From Fig. 5, both the positive and negative bands appeared for commercial collagen type I. A similar result was found for collagen type I extracted by U:LA (1:2), where a positive band, characteristic of the triple helix, was observed at  $222\text{ nm}$ . However, no positive band was found for collagen type I extracted by acetic acid, indicating that its triple helix was not preserved, due to the dissociation of intermolecular interactions<sup>29</sup> occurring when the control solvent was applied. Contrary to what happened to collagen extracted by acetic acid, the CD results confirmed the maintenance of

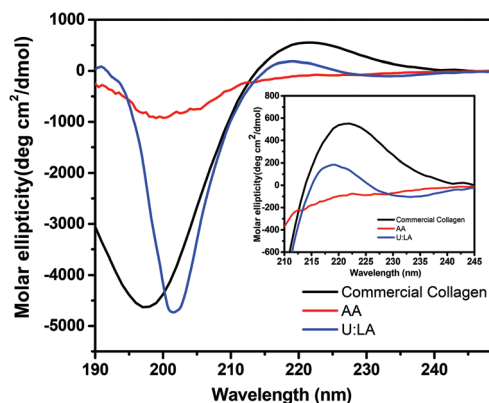


Fig. 5 Far-UV CD spectra of commercial collagen and collagen type I extracted from codfish skin using aqueous solutions of acetic acid and U:LA (1:2), obtained at  $4\text{ }^{\circ}\text{C}$ .

the triple helix of collagen type I extracted by U:LA (1:2), a result previously corroborated by FTIR. All the results allow us to conclude that the collagen type I extracted using U:LA (1:2) is not denatured.

#### Thermal stability of collagen extracted using U:LA (1:2)

The effect of temperature on the triple helix structure of collagen type I was also tested in the temperature range of 2 to 30 °C, at 220 nm (Fig. 6). The ellipticity of the positive peak decreased with an increase in temperature, proving that the triple helix structure of collagen is completely disturbed up to 10–11 °C. The collagen type I from codfish skins thermally denatures at 10.2 °C, a result in good agreement with findings previously reported in the literature for collagen from other fish species.<sup>44–46</sup> It was also found that, compared with mammalian sources, marine collagen has a lower thermal stability due to differences in the content of proline and hydroxyproline in their structures.<sup>45,46</sup>

Moreover, the thermal stability of collagen type I extracted from codfish skin wastes using U:LA (1:2) was reconfirmed by differential scanning calorimetry (DSC) (Fig. S5 from ESI†), where the melting temperature was found to be 10.5 °C.

#### XRD of collagen type I extracted using U:LA (1:2)

Fig. 7 shows the X-ray spectrum of the lyophilized collagen type I extracted using U:LA (1:2). Two diffraction peaks at diffraction angles ( $2\theta$ ) around 7.6° (representing the triple helix conformation) and 20° were identified, both characteristic of collagen.<sup>30,47</sup> Moreover, the same conclusion is made considering the similarity between the XRD patterns obtained for the commercial collagen and collagen type I extracted using an aqueous solution of U:LA (1:2).

#### Effect of the concentration of U:LA (1:2) on the extraction of collagen type I

After selecting the aqueous solution of U:LA (1:2) as the most efficient at extracting collagen type I from codfish skins

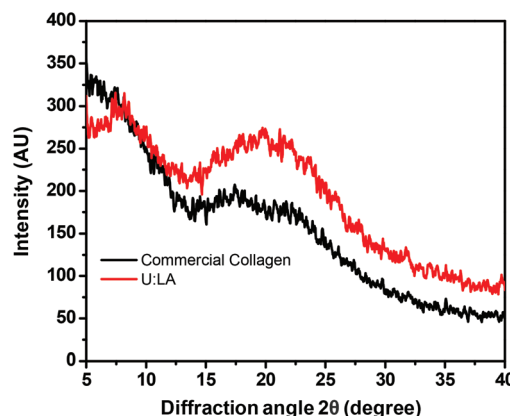


Fig. 7 XRD spectra of commercial collagen type I, and collagen extracted from codfish skin using AA and U:LA (1:2) at room temperature.

without compromising its chemical structure and thermal properties, its concentration in water was optimized. An initial screening with U:LA (1:2) at different concentrations from 0.15 to 1 M was performed, with the results depicted in Fig. 8. An increase in the concentration of U:LA (1:2) leads to an increase in the collagen type I extraction yield from 3.4 to 6.0%.

However, a decrease in the yield of extraction above 0.75 M was observed, which may be a result of the more acidic pH created when the DES concentration is increased (pH values in Fig. 9 – blue line). The extracted collagen samples were again characterized by FTIR (Fig. 9A) and SDS-PAGE (Fig. 9B). For all concentrations, and at room temperature, the collagen samples exhibited amide A, amide B, amide I, amide II, and amide III, as expected.

To confirm the purity of the extracted collagen, an SDS-PAGE was performed, where two clear bands attributed to  $\alpha$ -chains and one  $\beta$ -chain were found (Fig. 9B), thus demonstrating the typical result obtained for collagen type I. All the

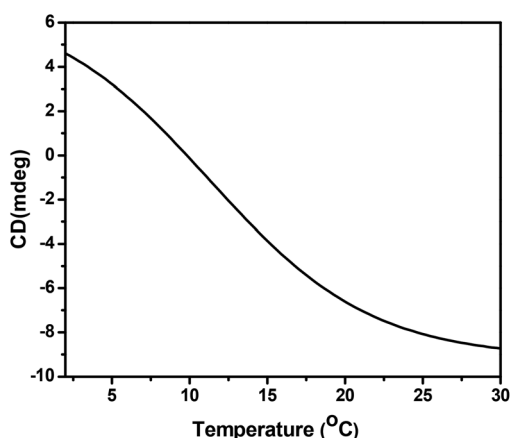


Fig. 6 Thermal denaturation curve of collagen type I from codfish skins extracted using an aqueous solution of U:LA (1:2) at 222 nm; heating rate of 0.1 °C min<sup>-1</sup>.

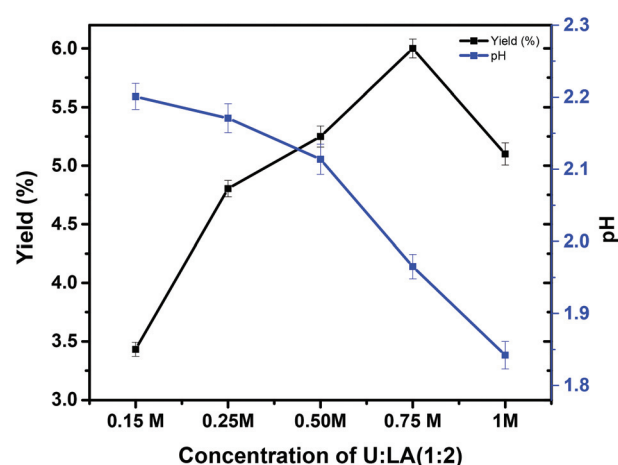


Fig. 8 pH and yield (%) of collagen type I obtained at various concentrations of U:LA (1:2) in water, for extractions done at 4 °C.

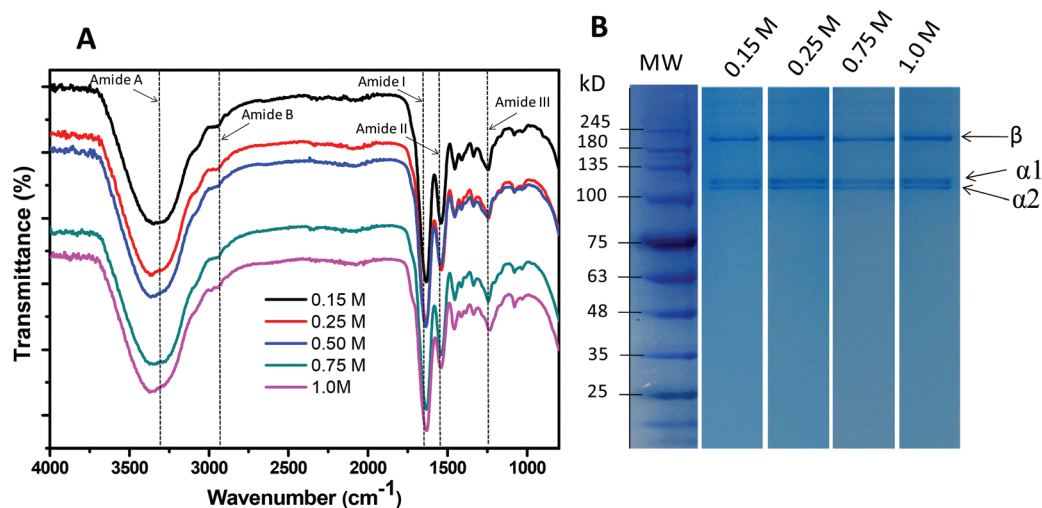


Fig. 9 Characterization of collagen extracted from the skin of codfish using U : LA (1 : 2) at different concentrations: (A) FTIR spectra; (B) SDS-PAGE.

results allow us to conclude that aqueous solutions of DES display much better performance in extracting pure collagen type I from codfish skins than the conventional approach using aqueous solutions of organic acids.

#### Environmental assessment

The three systems evaluated with LCA have distinct collagen yields and, therefore, the LCA results are expressed per 1 g of collagen obtained to allow a comparison of the environmental performance of those systems. The total impacts related with the environmental categories of global warming (equivalent to the carbon footprint), ozone formation, human health, terres-

trial acidification, mineral resource scarcity and fossil resource scarcity are shown in Table S5.† These results should be understood as worst-case scenarios, as electricity consumption is likely to be overestimated because it was calculated based on the nominal power of the equipment instead of being measured. The relative contributions of each input to the total impacts of each system are identified in Fig. 10. The highest impacts are obtained when acetic acid is used in collagen extraction. Extraction with U : LA (1 : 2) and U : PA (1 : 2) reduces the environmental impacts by 13–16% in all categories other than mineral resource scarcity in which the impacts decrease by only 4 and 10%, respectively, compared with AA

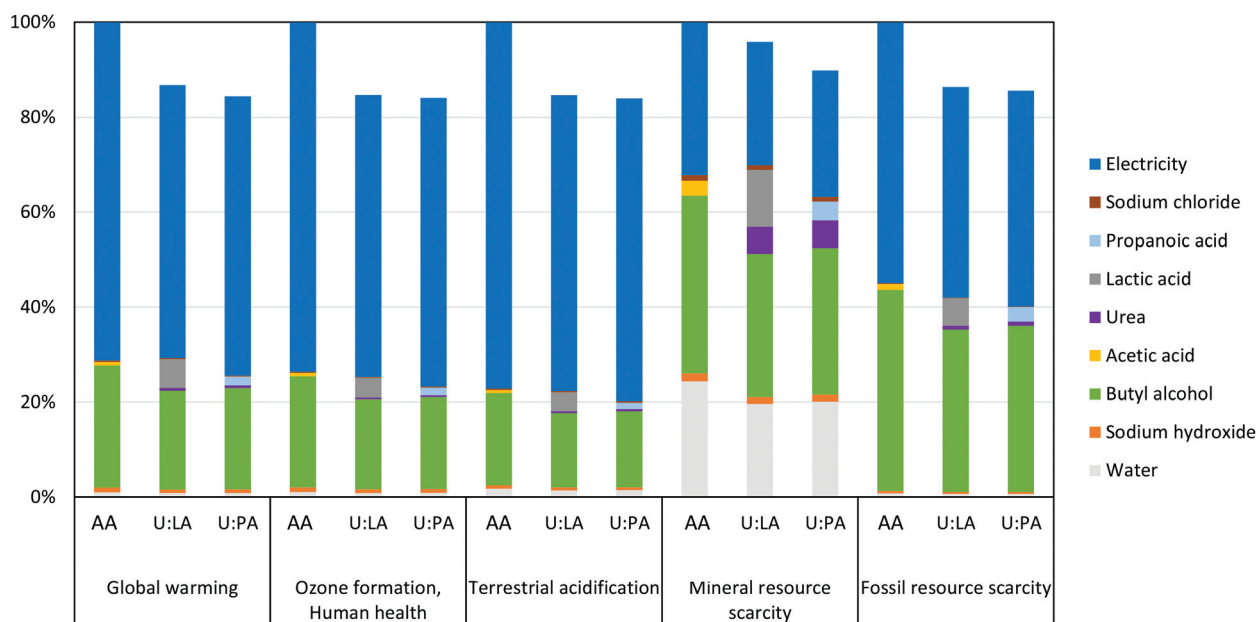


Fig. 10 LCA results for the three systems evaluated: one with only AA (conventional solvent), and two with DES, U : LA (1 : 2) and U : PA (1 : 2). 100% was assigned to the system with the largest result in each impact category.

(conventional solvent). The higher impacts of the conventional system result mainly from the lower collagen yield obtained. The system based on U : LA (1 : 2) has a slightly higher collagen yield, which leads to lower impacts in the steps of codfish skin preparation and collagen extraction (Fig. S6†) compared with the system using U : PA (1 : 2). Consequently, the system based on U : LA (1 : 2) has impacts similar to those of the system based on U : PA (1 : 2), although about 7% higher in the mineral resource scarcity category. It is no surprise that the step of collagen extraction and purification has the largest share of impacts followed by codfish skin preparation and, finally, solubilisation of collagen, for all impact categories and systems (Fig. S6†). Most of the total impacts of the three systems derive from electricity consumption (51–77%) followed by butyl alcohol consumption (19–42%), with the exception being mineral resource scarcity. In this category, 32–37% of the impacts come from butyl alcohol consumption, 27–32% from electricity consumption, and 16–19% from deionized water consumption. The mix of electricity production technology in Portugal was considered in the calculations, which includes almost 55% of renewable sources. The impacts can be reduced by changing the electricity mix. For example, if 100% photovoltaic electricity was consumed, the carbon footprint would be reduced by 64–69%.

## Conclusions

The sustainability of a process relies on its advantages in considering three main issues: (i) raw material(s), (ii) solvent(s) and technologies and (iii) final products. In this work, codfish skins, which are abundant waste from fish industries, were used as a source of collagen type I. An efficient, simple, and more environmentally friendly method to recover collagen using aqueous solutions of DES was successfully developed. Briefly, and after exploring the potential of different aqueous solutions of DES, the aqueous solution of U : LA (1 : 2) was selected as the most efficient. The extraction yield, the purity, chemical structure, and thermal stability of collagen obtained with U : LA (1 : 2) from codfish skins were far superior to those obtained in the conventional process using an aqueous solution of AA. This work is expected to contribute to the development of sustainable downstream processes positioned at the interface between green technology and blue economy, following the guidelines of the sustainable utilization of the oceans under the scope of a circular economy approach.

## Conflicts of interest

There are no conflicts of interest to declare.

## Acknowledgements

This work was developed within the scope of the projects CICECO-Aveiro Institute of Materials, UIDB/50011/2020 &

UIDP/50011/2020, and CESAM, UIDB/50017/2020 & UIDP/50017/2020, financed by national funds through the Portuguese Foundation for Science and Technology/MCTES. The authors also thank for the BPD funded project under PAC: Multipurpose strategies for the recovery of a wide range of agro-forestry and fisheries by-products: a step in the creation of an integrated biorefinery POCI-01-145-FEDER-016403 - SAICTPAC/0040/2015. M. Martins thanks FCT for the doctoral grant (SFRH/BD/122220/2016). A. Dias thanks FCT for her contract CEECIND/02174/2017.

## References

- 1 F. M. Kerton, Y. Liu, K. W. Omari and K. Hawboldt, *Green Chem.*, 2013, **15**, 860.
- 2 X. Cheng, Z. Shao, C. Li, L. Yu, M. A. Raja and C. Liu, *PLoS One*, 2017, **12**(1), e0169731.
- 3 D. J. Prockop and K. I. Kivirikko, *Annu. Rev. Biochem.*, 1995, **64**, 403–434.
- 4 J. A. Hodges and R. T. Raines, *J. Am. Chem. Soc.*, 2003, **125**, 9262–9263.
- 5 R. Radhakrishnan, P. Ghosh, T. A. Selvakumar, M. Shanmugavel and A. Gnanamani, *Adv. Tissue Eng. Regen. Med.*, 2020, **6**, 26–35.
- 6 J. K. Wang, K. P. Yeo, Y. Y. Chun, T. T. Y. Tan, N. S. Tan, V. Angeli and C. Choong, *Acta Biomater.*, 2017, **63**, 246.
- 7 L. Alves, A. L. P. Marques, E. Martins, T. H. Silva and R. L. Reis, *Cosmetics*, 2017, **4**, 39.
- 8 C. H. Lee, A. Singla and Y. Lee, *Int. J. Pharm.*, 2001, **221**, 1–22.
- 9 K. Silvipriya, K. K. Kumar, B. D. Kumar, A. John and P. Lakshmanan, *Curr. Trends Biotechnol. Pharm.*, 2016, **10**, 374–383.
- 10 M. C. G. Guillén, B. Giménez, M. E. L. Caballero and M. P. Montero, *Food Hydrocolloids*, 2011, **25**, 1813–1827.
- 11 M. Sadowska, I. Koodziejaska and C. Niecikowska, *Food Chem.*, 2003, **81**, 257–262.
- 12 J. Elango, B. Bin, B. Yongshi, Z. Yu, Z. Qingbo and W. Wenhui, *Mar. Drugs*, 2014, **12**, 3852–3873.
- 13 L. Wang, X. An, Z. Xin, L. Zhao and Q. Hu, *J. Food Sci.*, 2007, **72**, 450–455.
- 14 M. M. Schmidt, R. C. P. Dornelles, R. O. Mello, E. H. Kubota, M. A. Mazutti, A. P. Kempka and I. M. Demiate, *Int. Food Res. J.*, 2016, **23**, 913–922.
- 15 R. P. Bareil, R. Gauvin and F. Berthod, *Materials*, 2010, **3**, 1863–1887.
- 16 M. Raman and K. Gopakumar, *EC Nutrition*, 2018, **13**, 752–767.
- 17 E. Leikina, M. V. Merts, N. Kuznetsova and S. Leikin, *Proc. Natl. Acad. Sci. U. S. A.*, 2002, **99**, 1314–1318.
- 18 A. P. Abbott, D. Boothby, G. Capper, D. L. Davies and R. K. Rasheed, *J. Am. Chem. Soc.*, 2004, **126**, 9142–9147.
- 19 F. P. Pereira and J. Namiesnik, *ChemSusChem*, 2014, **7**, 1784–1800.
- 20 A. P. Abbott, G. Capper, D. L. Davies, R. K. Rasheed and V. Tambyrajah, *Chem. Commun.*, 2003, **99**, 70–71.



- 21 H. Passos, M. G. Freire and J. A. P. Coutinho, *Green Chem.*, 2014, **16**, 4786–4815.
- 22 V. Vieira, M. A. Prieto, L. Barros, J. A. P. Coutinho, I. C. F. R. Ferreira and O. Ferreira, *Ind. Crops Prod.*, 2018, **115**, 261–271.
- 23 M. Ruesgas-Ramón, M. C. Figueroa-Espinoza and E. Durand, *J. Agric. Food Chem.*, 2017, **65**, 3591–3601.
- 24 B. Soares, D. J. P. Tavares, J. L. Amaral, A. J. D. Silvestre, C. S. R. Freire and J. A. P. Coutinho, *ACS Sustainable Chem. Eng.*, 2017, **5**, 4056–4065.
- 25 C. Bai, Q. Wei and X. Ren, *ACS Sustainable Chem. Eng.*, 2017, **5**, 7220–7227.
- 26 A. Triolo, F. L. Celso, M. Brehm, V. D. Lisio and O. Russina, *J. Mol. Liq.*, 2021, **331**, 115750.
- 27 T. Nagai and N. Suzuki, *Food Chem.*, 2000, **68**, 277–281.
- 28 L. Alves, A. L. P. Marques, E. Martins, T. H. Silva and R. L. Reis, *Cosmetics*, 2017, **4**, 39.
- 29 A. M. Carvalho, A. P. Marques, T. H. Silva and R. L. Reis, *Mar. Drugs*, 2018, **16**, 495.
- 30 G. Wernet, C. Bauer, B. Steubing, J. Reinhard, E. Moreno-Ruiz and B. Weidema, *Int. J. Life Cycle Assess.*, 2016, **21**, 1218–1230.
- 31 M. A. J. Huijbregts, Z. J. N. Steinmann, P. M. F. Elshout, G. Stam, F. Verones, M. Vieira, M. Zipp, A. Hollander and R. van Zelm, *Int. J. Life Cycle Assess.*, 2017, **22**, 138–147.
- 32 B. B. Doyle, E. G. Bendit and E. R. Blout, *Biopolymers*, 1975, **14**, 937–957.
- 33 E. Skierka and M. Sadowska, *Food Chem.*, 2007, **105**, 1302–1306.
- 34 A. Veeruraj, M. Arumugam, T. Ajithkumar and T. Balasubramanian, *J. Mater. Sci. Mater. Med.*, 2012, **23**, 1729–1738.
- 35 R. Duan, J. Zhang, X. Du, X. Yao and K. Konno, *Food Chem.*, 2009, **112**, 702–706.
- 36 T. Nagai, E. Yamashita, K. Taniguchi, N. Kanamori and N. Suzuki, *Food Chem.*, 2001, **72**, 425–429.
- 37 L. Wang, X. An, Z. Xin, L. Zhao and Q. Hua, *Food Chem.*, 2008, **108**, 616–623.
- 38 F. Pati, B. Adhikari and S. Dhara, *Bioresour. Technol.*, 2010, **101**, 3737–3742.
- 39 A. A. Barros, I. M. Aroso, T. H. Silva, J. O. F. Mano, A. R. C. Duarte and R. L. Reis, *ACS Sustainable Chem. Eng.*, 2015, **3**, 254–260.
- 40 J. K. Lee, S. I. Kang, Y. J. Kim, M. J. Kim, M. S. Heu, B. D. Choi and J.-S. Kim, *Food Sci. Biotechnol.*, 2016, **25**, 131–136.
- 41 H. Liu, D. Li and S. Guo, *Food Chem.*, 2007, **101**, 621–625.
- 42 J. Bailey and N. D. Light, *Elsevier Applied Science*, New York, 1989.
- 43 G. Sotelo, M. B. Comesaña, P. R. Ariza and R. I. P. Martín, *J. Aquat. Food Prod. Technol.*, 2015, **25**, 388–399.
- 44 R. Tylingo, S. Mania, A. Panek, R. Piątek and R. Pawłowicz, *J. Biotechnol. Biomater.*, 2016, **6**, 234.
- 45 A. Karim and R. Bhat, *Food Hydrocolloids*, 2009, **23**, 563–576.
- 46 M. G. Guillén, B. Giménez, M. López-Caballero and M. Montero, *Food Hydrocolloids*, 2011, **25**, 1813–1827.
- 47 F. Zhang, A. Wang, Z. Li, S. He and L. Shao, *Food Nutr. Sci.*, 2011, **2**, 818–823.