



Showcasing research from Prof. Mingxian Liu's laboratory,  
School of Chemical Science and Engineering, Tongji  
University, Shanghai, China.

*In situ* Nafion-nanofilm oriented (002) Zn electrodeposition  
for long-term zinc-ion batteries

Our study introduces perfluoropolymer (Nafion) into aqueous electrolyte to activate a thermodynamically ultrastable Zn/electrolyte interface. This ultrathin artificial solid electrolyte interface with zincophilic  $-\text{SO}_3^-$  groups guides the directional  $\text{Zn}^{2+}$  electrodeposition along the (002) crystal surface even at high current density, yielding a dendrite-free Zn anode for propelling high-performance zinc-ion batteries.

As featured in:



See Mingxian Liu *et al.*,  
*Chem. Sci.*, 2024, **15**, 4322.

Cite this: *Chem. Sci.*, 2024, 15, 4322

All publication charges for this article have been paid for by the Royal Society of Chemistry

## *In situ* Nafion-nanofilm oriented (002) Zn electrodeposition for long-term zinc-ion batteries†

Da Zhang,<sup>a</sup> Ziyang Song,<sup>a</sup> Ling Miao,<sup>a</sup> Yaokang Lv,<sup>b</sup> Lihua Gan<sup>b</sup> and Mingxian Liu<sup>b</sup>\*<sup>a</sup>

Dendrite growth and parasitic reactions of a Zn metal anode in aqueous media hinder the development of up-and-coming Zn-ion batteries. Optimizing the crystal growth after Zn nucleation is promising to enable stable cyclic performance of the anode, but directly regulating specific crystal plane growth for homogenized Zn electrodeposition remains highly challenging. Herein, a perfluoropolymer (Nafion) is introduced into an aqueous electrolyte to activate a thermodynamically ultrastable Zn/electrolyte interface for long-term Zn-ion batteries. The low adsorption energy (−2.09 eV) of Nafion molecules on Zn metal ensures the *in situ* formation of a Nafion-nanofilm during the first charge process. This ultrathin artificial solid electrolyte interface with zincophilic −SO<sub>3</sub><sup>−</sup> groups guides the directional Zn<sup>2+</sup> electrodeposition along the (002) crystal surface even at high current density, yielding a dendrite-free Zn anode. The synergic Zn/electrolyte interphase electrochemistry contributes an average coulombic efficiency of 99.71% after 4500 cycles for Zn||Cu cells, and Zn||Zn cells achieve an ultralong lifespan of over 7000 h at 5 mA cm<sup>−2</sup>. Besides, Zn||MnO<sub>2</sub> cells operate well over 3000 cycles. Even at −40 °C, Zn||Zn cells achieve stable Zn<sup>2+</sup> plating/stripping for 1200 h.

Received 25th December 2023

Accepted 20th February 2024

DOI: 10.1039/d3sc06935d

rsc.li/chemical-science

## Introduction

Aqueous zinc-ion batteries (ZIBs) have emerged as one of the advanced electrochemical energy storage systems, characterized by their excellent safety, low cost, and high energy and power densities (820 mA h g<sup>−1</sup> and 5855 mA h cm<sup>−3</sup>).<sup>1–6</sup> However, the Zn metal anode in ZIBs encounters significant challenges, including the formation of disordered dendrites and grievous interface polarization reactions (Zn anode corrosion and hydrogen evolution), which restrict cycling performance.<sup>7–12</sup> Conspicuously, the low plating/stripping efficiency of the anode at high current densities (≥5 mA cm<sup>−2</sup>) and in low-concentration Zn salt (1 M and below) significantly hinders the practical application of ZIBs.<sup>13–16</sup> Typically, protecting the Zn anode by organic–inorganic composite coating is an effective strategy, but the slow ion transport caused by the thicker organic hydrophobic layer limits the diffusion of Zn<sup>2+</sup> at the solid phase interface (SEI), resulting in an increase in the nucleation potential of Zn<sup>2+</sup> ions. Besides, organic co-solvents disrupt the hydrogen bonding network of the electrolyte and reduce the ionic conductivity of the original electrolyte.

Accordingly, it is necessary to achieve deposition induction and rapid diffusion of Zn<sup>2+</sup> ions.

Profiting from the stable structure and the abundant zincophilic groups, polymers are widely used as electrode protective layers and electrolyte additives to deliver a widened electrochemical window and accelerate the dissociation of Zn salts.<sup>17–22</sup> As a common cation transfer polymer separator, the protons of Nafion are gradually replaced by Zn<sup>2+</sup> as the cycling proceeds, causing uniform Zn<sup>2+</sup> transport at the electrode/electrolyte interface. Specifically, Nafion is combined with zeolite through a solution pouring method to construct an organic–inorganic layer, where the zincophilic Nafion benefits the transport of zinc ions and inorganic zeolites with 0.74 nm micropores inhibit the side reactions at the anode/electrolyte interface to prevent dendrite growth.<sup>23</sup> However, such pouring strategy generally yields a micrometer-scale protective layer which is not conducive to the rapid plating/stripping of zinc ions.<sup>24–29</sup> Beyond that, the present Nafion-based layer at the Zn anode often results in uncontrollable Zn nucleation with a (101) and (110)-dominated texture due to high Zn<sup>2+</sup> concentration polarization, causing deteriorated hydrogen evolution reaction (HER) and loose Zn plating.<sup>30–32</sup> In contrast, the (002) crystal plane is the most stable texture due to its lowest surface nucleation energy, which can homogenize the Zn electrodeposition to suppress the growth of dendrites and HER reactions, achieving long-term ZIBs.<sup>33–35</sup> Therefore, reducing the thickness of the Nafion-based protective layer from the micrometer to nanometer for rapid plating/stripping of zinc ions,

<sup>a</sup>Shanghai Key Lab of Chemical Assessment and Sustainability, School of Chemical Science and Engineering, Tongji University, Shanghai, 200092, P. R. China. E-mail: liumx@tongji.edu.cn

<sup>b</sup>College of Chemical Engineering, Zhejiang University of Technology, Hangzhou 310014, P. R. China

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3sc06935d>





accompanied by decreasing the surface nucleation energy for achieving stable Zn electrodeposition to inhibit the HER is expected to boost the anode reversibility and long-term ZIBs, yet not reported.

In this work, we introduce perfluoropolymer (Nafion) molecules to construct an anode micro-electric field and activate a thermodynamically ultrastable zinc anode/electrolyte interface for propelling high-performance ZMBs. The spontaneous adsorption of Nafion (NAF) molecules on the Zn anode ensures the *in situ* generation of zincophilic NAF-film, which regulates the directional and dendrite-free deposition of solvated  $\text{Zn}^{2+}$  ions, significantly improving the plating/stripping efficiency of the Zn anode. Therefore, Zn||Zn cells using a  $\text{Zn}(\text{OTF})_2$ -NAF ( $\text{OTF}^- = \text{CF}_3\text{SO}_3^-$ ) electrolyte can cycle over 5000 h, and Zn||Cu cells achieve an average CE of 99.71% after 4500 cycles at 5 mA  $\text{cm}^{-2}$ . Significantly, Zn|| $\text{MnO}_2$  cells exhibit remarkable cyclic stability over 3000 cycles. Even at  $-40^\circ\text{C}$ , the reversible plating/stripping of Zn||Zn cells can work over 1200 h. This work offers a design avenue of dendrite-free Zn deposition for ultrastable ZMBs.

## Results and discussion

First-principles calculations and systemic experiments were performed to study the  $\text{Zn}^{2+}$  transport mechanisms in  $\text{Zn}(\text{OTF})_2$ - $\text{H}_2\text{O}$  and  $\text{Zn}(\text{OTF})_2$ -NAF electrolytes.<sup>36–39</sup> For the  $\text{Zn}(\text{OTF})_2$ - $\text{H}_2\text{O}$  electrolyte interface (Fig. 1a), when the solvated  $\text{Zn}^{2+}$  ions migrate to the anode/electrolyte interface, the inhomogeneous  $\text{Zn}^{2+}$  plating and  $\text{Zn}(\text{OTF})_2$  decomposition result in potential differentiation at the Zn anode, further leading to the fracturing of the SEI and the generation of  $\text{H}_2$  (Fig. S1†). In comparison, NAF molecules show a high binding energy with Zn metal (Fig. S2–S4 and Table S1†), which indicates their great predilection to form a NAF-nanofilm on the Zn anode.<sup>40–45</sup> The unique  $-\text{SO}_3^-$  functional groups in NAF molecules accept  $\text{Zn}^{2+}$  ion transportation to the anode interface, avoiding excessive plating on the Cu collector. When a smooth NAF-nanofilm is formed at the anode/electrolyte interface (Fig. 1b), the Zn anode exhibits dense  $\text{Zn}^{2+}$  plating even at high current densities.

The ionic conductivity of  $\text{Zn}^{2+}$  ions in various electrolytes was analyzed by electrochemical impedance spectroscopy (EIS) using the formula  $\sigma = L/RS$  (where  $L$ ,  $R$ , and  $S$  are the separator thickness, bulk resistance, and area, respectively). The  $\text{Zn}(\text{OTF})_2$ -NAF electrolyte shows the smallest resistance of 3.7  $\Omega$  (Fig. 1c), corresponding to the fastest  $\text{Zn}^{2+}$  conductivity of  $1.22 \times 10^{-2} \text{ S cm}^{-1}$  (Table S2†). The cyclic voltammetry (CV) curves of Zn||Cu cells show the enhancement of Zn ion transport kinetics by the  $\text{Zn}(\text{OTF})_2$ -NAF electrolyte. With the increase of scan rate from 1 to 4 mV  $\text{s}^{-1}$ , the thicker SEI affects the transfer rate of  $\text{Zn}^{2+}$  ions, resulting in lower plating/stripping efficiency in the  $\text{Zn}(\text{OTF})_2$ - $\text{H}_2\text{O}$  electrolyte (Fig. S5†). Compared to the  $\text{Zn}(\text{OTF})_2$ - $\text{H}_2\text{O}$  electrolyte, the higher amount of  $\text{Zn}^{2+}$  ions transported in the  $\text{Zn}(\text{OTF})_2$ -NAF electrolyte (0.85 vs. 0.33) also demonstrates the rapid transfer and storage of  $\text{Zn}^{2+}$  ions in the solid/liquid phase interface (Fig. S6†). Of note, there is no significant polarization reaction at the Zn anode demonstrating stable  $\text{Zn}^{2+}$  plating/stripping.

The X-ray diffraction (XRD) patterns of the Cu substrate of Zn||Cu cells after cycling at 1 mA  $\text{cm}^{-2}$  in various electrolytes show obviously different  $\text{Zn}^{2+}$  plating/stripping (Fig. 1d). Fig. 1e demonstrates the geometric models of charge distributions at the Zn/electrolyte interface. Among different Zn/electrolyte interfaces, Zn-NAF interaction and significant charge transfer induce a larger binding energy of  $\text{Zn}(\text{OTF})_2$ , which accelerates the interfacial  $\text{Zn}^{2+}$  transfer. The Zn deposited through the NAF-nanofilm, unlike the previous Nafion-zeolite protective layer,<sup>46–51</sup> preferentially grows along the (002) crystal surface to form a dense anode after 200 h, due to a lower binding energy of the NAF-nanofilm and zinc metal anode (Fig. 1f).<sup>52</sup> Notably, the charge density of  $\text{Zn}^{2+}$  ions deposited in the  $\text{Zn}(\text{OTF})_2$ -NAF electrolyte is more uniform compared to that in the  $\text{Zn}(\text{OTF})_2$ - $\text{H}_2\text{O}$  electrolyte, which is crucial for dense Zn nucleation and a dendrite-free anode (Fig. 1g). Even when the plating/stripping continues for 2000 h,  $\text{Zn}^{2+}$  ions still preferentially nucleate along the (002) crystal plane (Fig. S7†).

The  $\text{Zn}^{2+}$  deposition evolution in electrolytes was analyzed by field emission scanning electron microscopy (SEM) and transmission electron microscopy (TEM). For the  $\text{Zn}(\text{OTF})_2$ - $\text{H}_2\text{O}$  electrolyte (Fig. 1h), a large amount of blocky Zn appeared on the Cu substrate after a plating/stripping of 24 h. As the operating time increases to 200 h, the irregular growth of dendrites on the Zn anode inevitably leads to SEI damage and  $\text{Zn}(\text{OTF})_2$  consumption (Fig. S8†). In contrast, the deposition morphology in the  $\text{Zn}(\text{OTF})_2$ -NAF electrolyte is smoother (predominantly hexagonal deposition), maintaining a stable (002) crystal growth (Fig. 1i). The interface of directional crystal growth ((002) plane) reduces the formation of dendrites and delays the corrosion rates of Zn anodes (Fig. S9 and S10†). TEM images clearly show the plating of  $\text{Zn}^{2+}$  in different electrolytes. With a lower current density (1 mA  $\text{cm}^{-2}$  and 0.5 mA h  $\text{cm}^{-2}$ ), an inhomogeneous SEI was obtained on the Zn anode, about 480 and 570 nm (Fig. 1j). Besides, obvious fluctuations occur at the Zn anode interface at 5 mA  $\text{cm}^{-2}$  (Fig. S11†), resulting in uneven SEI thickness and disordered Zn deposition. Notably, the NAF-nanofilm (15 nm in thickness) and SEI (100 nm in thickness) can be observed at the interface between the anode and electrolyte (Fig. 1k), which promises high-kinetics  $\text{Zn}^{2+}$  transfer. Even at 10 mA  $\text{cm}^{-2}$ , the SEI in the  $\text{Zn}(\text{OTF})_2$ -NAF electrolyte maintains higher crystallinity compared to that in the  $\text{Zn}(\text{OTF})_2$ - $\text{H}_2\text{O}$  electrolyte (Fig. S12†).

*Ab initio* molecular dynamics (AIMD) simulations and density functional theory (DFT) calculations were used to explore the solvation structure and coordination potential during the (dis)charging of ZIBs. For 2 M  $\text{Zn}(\text{OTF})_2$ - $\text{H}_2\text{O}$  electrolyte (Fig. 2a and S13†), the  $\text{Zn}^{2+}$  solvation structure includes five  $\text{H}_2\text{O}$  molecules and one  $\text{OTF}^-$  ion. The more solvated the  $\text{H}_2\text{O}$  molecules, the more severe the hydrogen evolution reactions (Fig. S14–16†). Consequently, NAF co-migrated with  $\text{Zn}^{2+}$  ions to form a NAF-nanofilm on the Zn anode, effectively guiding the stable deposition of  $\text{Zn}^{2+}$  ions (Fig. 2b). Compared with the  $\text{Zn}(\text{OTF})_2$ - $\text{H}_2\text{O}$  electrolyte, the solvated structure of the  $\text{Zn}(\text{OTF})_2$ -NAF electrolyte indicates the decreased proportion of  $\text{H}_2\text{O}$  molecules around  $\text{Zn}^{2+}$  ions in the solvated shell (Fig. 2c and d). According to molecular dynamics simulations,<sup>53</sup> the



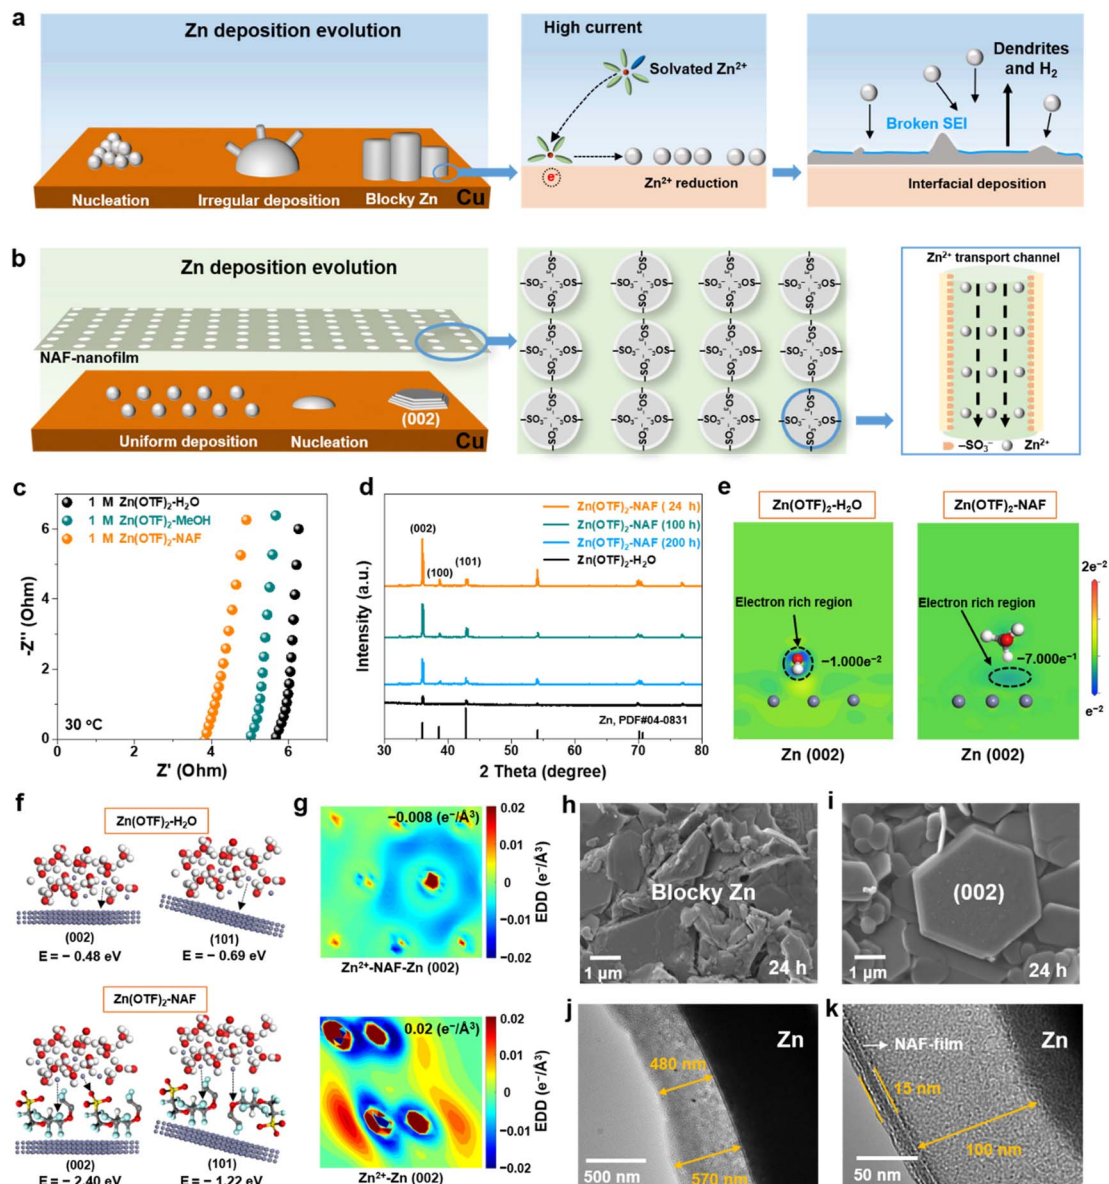


Fig. 1 Schematic diagrams of  $\text{Zn}^{2+}$  deposition in (a)  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  and (b)  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolytes. (c) Ionic conductivities of various electrolytes. (d) XRD patterns after  $\text{Zn}^{2+}$  plating/stripping with different electrolytes. (e) Charge distribution at different anode/electrolyte interfaces. (f) Interfacial charge transfer on different crystal planes. (g) The electron density difference of the Zn anode after  $\text{Zn}^{2+}$  plating on the (002) crystal plane. SEM images of  $\text{Zn}^{2+}$  plating/stripping evolution after 24 h in (h)  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  and (i)  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolytes. TEM images of SEI thickness at  $1 \text{ mA cm}^{-2}$  in (j)  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  and (k)  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolytes.

coordination probability of  $\text{OTF}^-$  with  $\text{Zn}^{2+}$  in the  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolyte is significantly higher than that in the  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  electrolyte, triggering favorable solvated environments to limit the hydrogen evolution reaction of  $\text{H}_2\text{O}$  molecules, and boosting the  $\text{Zn}^{2+}$  plating/stripping efficiency at high current densities. The chemical components on the surface of the Zn anode were detected by  $\text{Ar}^+$  sputtering X-ray photoelectron spectroscopy (XPS). To maintain the uniformity and integrity of the SEI, all cells were subjected to two constant-current (dis)charging cycles. The elemental contents of the SEI show significant differences for different electrolytes (Fig. S17<sup>†</sup>). For the  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  electrolyte, the inorganic components in the SEI

are mainly  $\text{ZnCO}_3$ ,  $\text{ZnO}$ ,  $\text{ZnF}_2$ , and  $\text{ZnS}$  (Fig. 2e). Notably,  $\text{ZnF}_2$  almost disappears with the increase of sputtering time (20 and 40 s), indicating the scarcity of high  $\text{Zn}^{2+}$  conductivity components in the SEI, and the uneven SEI impedes the rapid transfer and plating/stripping of  $\text{Zn}^{2+}$ . The detected characteristic peak of  $\text{OTF}^-$  confirms the continuous decomposition of  $\text{Zn}(\text{OTF})_2$  during the (dis)charging of ZIBs.<sup>54</sup>

For  $\text{Zn}(\text{OTF})_2\text{-MeOH}$  ( $\text{MeOH} = \text{methanol}$ ) electrolyte (Fig. S18<sup>†</sup>),  $\text{ZnF}_2$  (684.8 eV) and  $^*\text{CF}_3$  (689.4 eV)<sup>55</sup> can be captured after the etching time reaches 20 s (Table S3<sup>†</sup>). The results indicate the formation of a  $\text{ZnF}_2$  and  $\text{ZnCO}_3$  polycrystalline phase SEI. However, the solvation structure of  $\text{Zn}^{2+}$



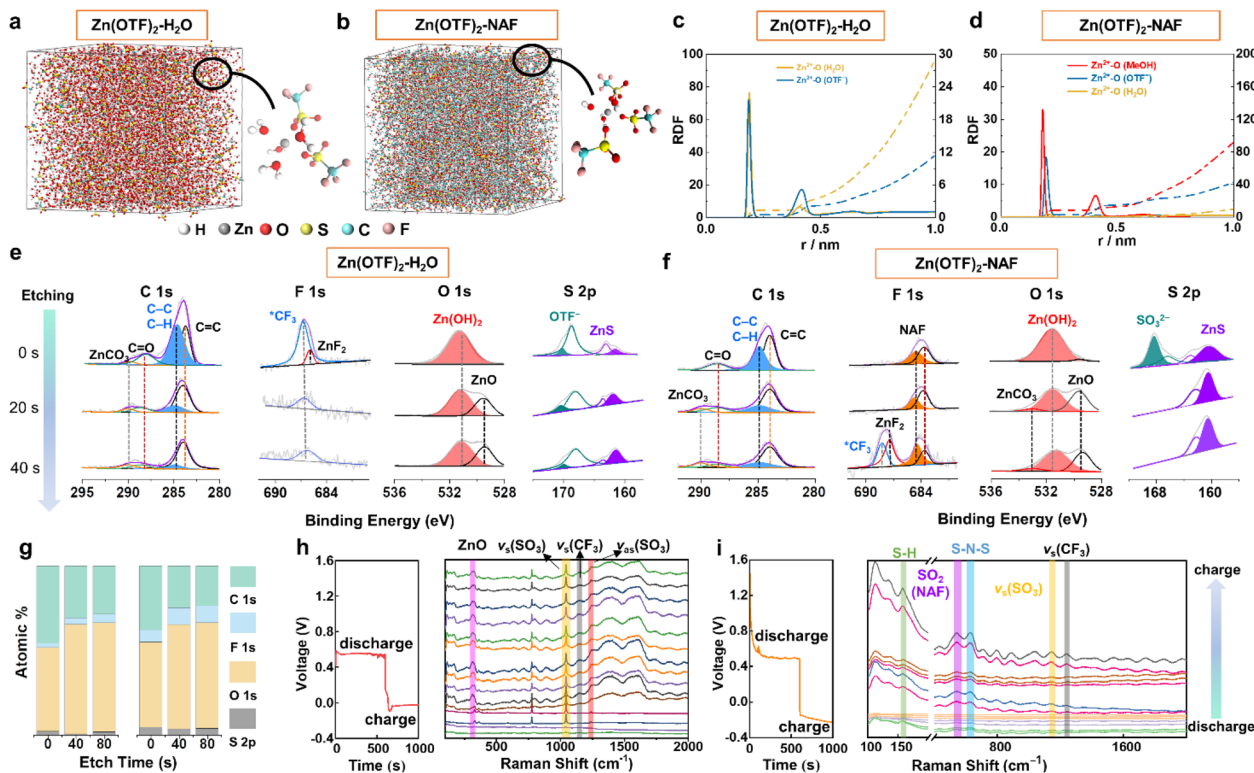


Fig. 2 (a and b) 3D snapshots and corresponding enlarged images of solvation sheaths, and (c and d) radial distribution functions of  $\text{Zn}^{2+}\text{-O}$  in  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  and  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolytes. (e and f) In-depth XPS spectra analysis of different electrolytes. (g) The atomic concentration percentages corresponding to different SEIs. *In situ* Raman test of  $\text{Zn}||\text{Cu}$  cells in (h)  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  and (i)  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolytes.

ions in the  $\text{Zn}(\text{OTF})_2\text{-MeOH}$  electrolyte damages the formed SEI and causes sustained consumption of  $\text{Zn}(\text{OTF})_2$ , restricting the long-term cycling performance of ZIBs. Therefore, specific protection needs to be implemented for the Zn anode. Even when the etching time reaches 40 s, the detected  $\text{ZnF}_2$  confirms that NAF-SEI has a more complete polycrystalline phase structure (Fig. 2f). As the sputtering time increases, the  $\text{SO}_3^-$  fraction of NAF is captured on the Zn surface, which verifies the self-adsorption of NAF with Zn.<sup>56</sup> Besides, the protection of the NAF-nanofilm on the Zn anode is confirmed by the disappearance of  $\text{OTF}^-$  ions. Fig. 2g shows the variation in elemental content of the formed SEI in different electrolytes. The introduction of NAF solution increases the ratio of  $\text{ZnF}_2$  and  $\text{ZnCO}_3$  content in the SEI.

*In situ* Raman spectroscopy was applied to monitor the Raman peak variations of the Zn anode in the  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  electrolyte (Fig. S19<sup>†</sup>). During discharging ( $\text{Zn}^{2+}$  migrating to the Cu collector), a significant  $\text{Zn}(\text{OTF})_2$  component is detected, which is reflected by the peaks at 1036 and 1256  $\text{cm}^{-1}$  (Fig. 2h).<sup>57</sup> The characteristic peak of  $\text{Zn}(\text{OTF})_2$  (1224  $\text{cm}^{-1}$ )<sup>58</sup> is accurately observed, further confirming the severe hysteresis in the desolvation process of  $\text{Zn}(\text{OTF})_2$ . For the  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolyte, a noticeable voltage drop at the beginning of the voltage–time curve is attributed to the binding between NAF and Zn (Fig. 2i). Besides, the S–H binding sites of NAF at 156  $\text{cm}^{-1}$  are captured.<sup>59</sup> The characteristic peaks of  $\nu_s(\text{SO}_3)$  and  $\nu_{as}(\text{SO}_3)$  derived from  $\text{Zn}(\text{OTF})_2$  can be detected in the  $\text{Zn}(\text{OTF})_2\text{-}$

$\text{H}_2\text{O}$  electrolyte, confirming the precipitation of a large amount of  $\text{Zn}(\text{OTF})_2$ . In contrast, the characteristic peak of  $\text{Zn}(\text{OTF})_2$  in the  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolyte is very weak, indicating little  $\text{Zn}(\text{OTF})_2$  precipitates at the Zn/electrolyte interface and ensuring the long-term stability of ZIBs. The *in situ* attenuated total reflectance-Fourier transform infrared (ATR-FTIR) spectroscopy was utilized to analyse the evolution pattern of the solvation conformation in electrolytes (Fig. 3a). The process of  $\text{Zn}^{2+}$  plating/stripping was studied under constant-current density (1  $\text{mA cm}^{-2}$ ) (dis)charging. An obvious  $\text{OTF}^-$  peak (1032  $\text{cm}^{-1}$ ) is captured during discharging (Fig. 3b and S20<sup>†</sup>), indicating that  $\text{OTF}^-$  molecules remain at the anode/electrolyte interface during  $\text{Zn}^{2+}$  stripping.

In the voltage–time curves of  $\text{Zn}^{2+}$  plating/stripping, the cell using the  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  electrolyte has a higher overpotential than that using  $\text{Zn}(\text{OTF})_2\text{-NAF}$ . A sharp increase in voltage (0.0958 V) is even observed at the end of the charging process (voltage–time curve constant coordinate for 1.7 h, Fig. 3b), which is attributed to the precipitation and decomposition of  $\text{Zn}(\text{OTF})_2$ , leading to an increase in the proportion of  $\text{H}_2\text{O}$  molecules around solvated  $\text{Zn}^{2+}$  ions, producing more hydrogen gas. Besides, the reversible change of MeOH molecules during (dis)charging indicates the rapid migration of  $\text{Zn}^{2+}$  ions (Fig. 3c). More importantly, the appearance of the C=O peak suggests a possible bimolecular Cannizzaro disproportionation of MeOH molecules to form methoxy, followed by dehydrogenation to  $\text{CH}_2\text{O}^-$ . The generated  $\text{CH}_2\text{O}^-$  promotes a charge-rich





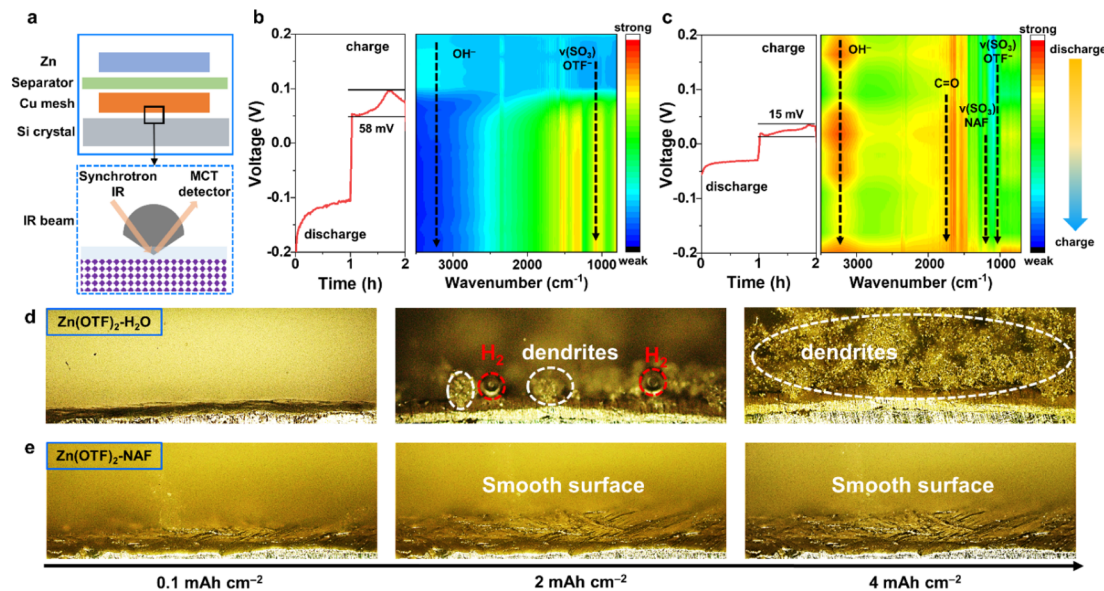


Fig. 3 (a) Schematic diagram of *in situ* ATR-FTIR analysis. (b and c) Voltage–time curves and corresponding ATR-FTIR characterizations in  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  and  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolytes. *In situ* DOF microscope plating images in (d)  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  and (e)  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolytes.

state in the solvation sheath of  $\text{Zn}^{2+}$  ions and shields it from  $\text{H}_2\text{O}$  molecules, which is crucial for rapid  $\text{Zn}^{2+}$  transport.<sup>60–62</sup> The dendrite growth and hydrogen production on the Zn anode were directly observed through *in situ* depth of field (DOF) microscopy. For the  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  electrolyte, the generation of bubbles can be observed when the  $\text{Zn}^{2+}$  plating capacity reaches  $0.1 \text{ mA h cm}^{-2}$  (Fig. 3d). As the discharging process continues, obvious gray-black dendrites appear on the Zn anode, accompanied by severe corrosion after deposition (Fig. S21†). Due to the direct contact between the Zn anode and electrolyte, similar phenomena can also be examined in the  $\text{Zn}(\text{OTF})_2\text{-MeOH}$  electrolyte (Fig. S22†). Without the regulation by the NAF-nanofilm, the  $\text{Zn}^{2+}$  transport kinetics is slower, and the growth of dendrites remains uncontrolled. Compared with the  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  electrolyte, the Zn corrosion can be delayed in the  $\text{Zn}(\text{OTF})_2\text{-MeOH}$  electrolyte because MeOH significantly reduces the proportion of active  $\text{H}_2\text{O}$  molecules in the solvation sheath of  $\text{Zn}^{2+}$  ions. No bubbles are observed when the plating capacity reaches  $4 \text{ mA h cm}^{-2}$ , and the color of the deposited Zn is almost the same as that of the original Zn (Fig. 3e). The *in situ* DOF plating results further indicate the substantially suppressed dendrite growth and  $\text{H}_2$  generation in the  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolyte.

Scanning probe microscopy (SPM) was applied to investigate the plating morphology and interface potential of the Zn anode.<sup>63</sup> Based on the working principle and test results of SPM, the calculation rules of the Zn anode interface potential are obtained:

$$\text{Test 1: } V_{\text{sample}} - V_{\text{tip}} = (\Phi_{\text{tip}} - \Phi_{\text{sample}})/e \quad (1)$$

$$\text{Test 2: } V_{\text{HOPG}} - V_{\text{tip}} = (\Phi_{\text{tip}} - \Phi_{\text{HOPG}})/e \quad (2)$$

$$e(\text{Test 1}) = \Phi_{\text{tip}} - \Phi_{\text{sample}} \quad (3)$$

$$e(\text{Test 2}) = \Phi_{\text{tip}} - \Phi_{\text{HOPG}} \quad (4)$$

Based on formulae (1) and (2), the conversion formulae (3) and (4) between the probe potential and the sample surface potential, and further formula (5) for calculating the surface potential of the sample can be obtained.  $\Phi_{\text{sample}}$  and  $\Phi_{\text{tip}}$  denote the test sample surface potential and probe tip potential, respectively.  $\Phi_{\text{HOPG}}$  is a fixed applied potential of 4.5 eV.

$$\Phi_{\text{sample}} = \Phi_{\text{HOPG}} + e(\text{Test 1} - \text{Test 2}) \quad (5)$$

The height difference of the Zn anode after plating reaches 1.81 and 2.95  $\mu\text{m}$  (plating capacities are 1 and 2  $\text{mA h cm}^{-2}$ ) in the  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  electrolyte (Fig. 4a), together with a minimum local potential value of  $-2.64 \text{ V}$  and a maximum value of  $0.93 \text{ V}$  through the interfacial potential distribution maps. In contrast, more uniform deposition and potential are achieved in the  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolyte, as reflected by the height difference of 1.36  $\mu\text{m}$  and the minimum potential value of  $-0.41 \text{ V}$  (Fig. 4b). As a result, the average surface potentials in  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  and  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolytes are determined to be 5.67 and 4.94 eV. The larger average potential on the sample surface indicates the more disordered interfacial charge distribution and irregular  $\text{Zn}^{2+}$  deposition. The fitted interfacial average potentials in the  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  electrolyte are 102.7 and 817.4 mV, which are inferior to those of the  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolyte (93.3 and 328.1 mV, Fig. 4c and d). The more homogeneous interfacial potential implies a lower activation energy for  $\text{Zn}^{2+}$  ion migration, thus enabling the dissociation of  $\text{Zn}(\text{OTF})_2$  at the Zn/NAF interface and accelerating the transport efficiency of  $\text{Zn}^{2+}$  ions.<sup>64,65</sup> Besides, the  $\text{Zn}^{2+}$  plating test in the  $\text{Zn}(\text{OTF})_2\text{-MeOH}$  electrolyte (Fig. S23†) confirms the attenuated desolvation of  $\text{Zn}^{2+}$  ions by the NAF-nanofilm. Without the protection of the NAF-nanofilm, the solvation effect remains the



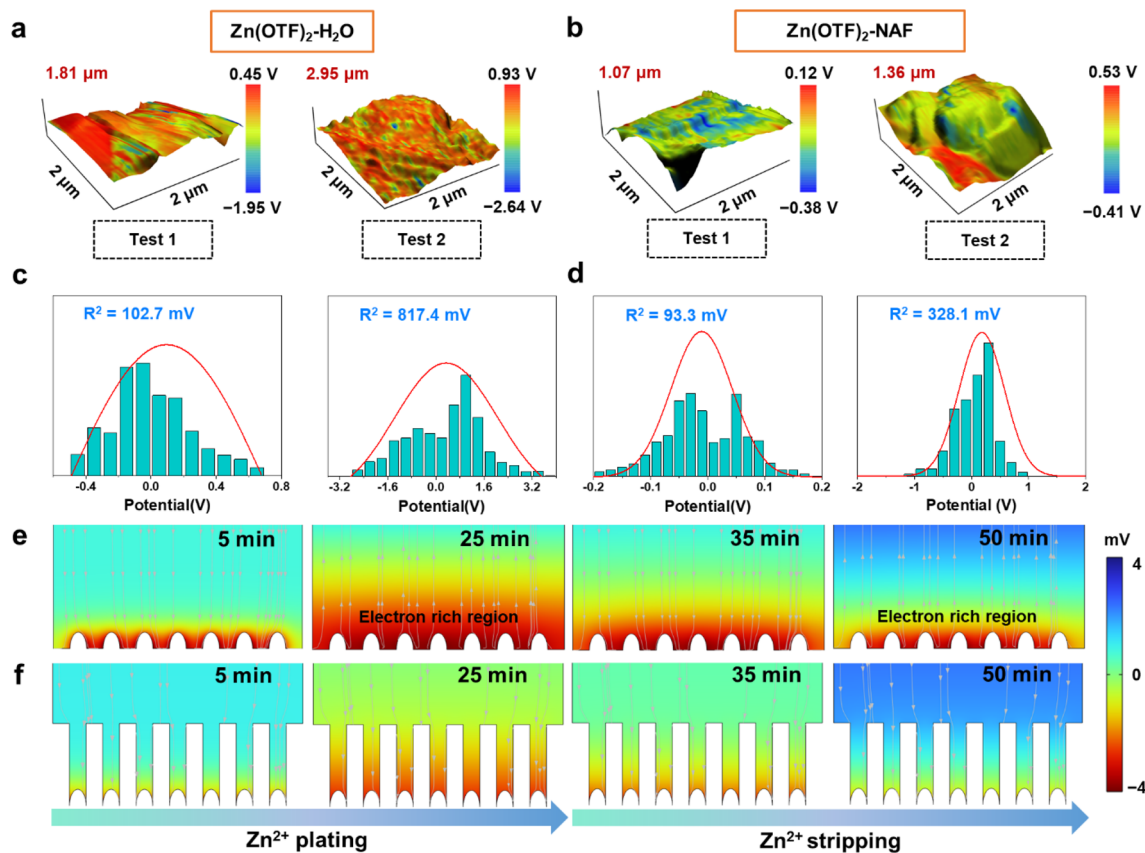


Fig. 4 (a and b) Potential distribution and height variation on the anode surface after  $\text{Zn}^{2+}$  plating in different electrolytes, tests 1 and 2 were  $\text{Zn}^{2+}$  plated to 1 and 2  $\text{mA h cm}^{-2}$ , respectively (the current density was  $0.5 \text{ mA cm}^{-2}$ ). Gaussian statistical distribution of the interfacial potential in (c)  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  and (d)  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolytes. Simulation of the potential evolution of  $\text{Zn}^{2+}$  plating/stripping in (e)  $\text{Zn}/\text{electrolyte}$  and (f)  $\text{Zn-NAF}/\text{electrolyte}$  interfaces.

main reason for the slow  $\text{Zn}^{2+}$  plating/stripping. Based on the deposition potential analysis, the potential simulation of the  $\text{Zn}^{2+}$  plating/stripping process was performed through the COMSOL potential field.<sup>66</sup> During  $\text{Zn}^{2+}$  plating (from 5 to 25 min) in  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  electrolyte, a local micro-electric field is formed due to the polarization of the electrolyte concentration near the Zn anode (Fig. 4e), which exacerbates the hydrogen evolution reaction (HER) of solvation  $\text{H}_2\text{O}$  molecules and dendrite growth. The potential gradient near the Zn anode remains less than 0 mV during the stripping (35 to 50 min). In the  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolyte, a microporous film (NAF-nanofilm) is formed on the Zn anode, and the migration of  $\text{Zn}^{2+}$  is induced by  $-\text{SO}_3\text{F}$  groups on the NAF-nanofilm. The solvation structure fails to reach the Zn anode (Fig. 4f), resulting in a smaller potential gradient compared with the  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  electrolyte after 25 min. During  $\text{Zn}^{2+}$  stripping from the anode interface (35 to 50 min), the potential gradient response of the  $\text{Zn}/\text{NAF}/\text{electrolyte}$  interface is faster than that of  $\text{Zn}/\text{electrolyte}$ , which is attributed to the rapid co-migration of dissociated  $\text{Zn}(\text{OTF})_2$  with the solvated structure. For the  $\text{ZnSO}_4\text{-NAF-H}_2\text{O}$  electrolyte (Fig. S24–S27<sup>†</sup>), the micro-electric field constructed by the NAF-nanofilm also enhances the electrochemical performance of ZIBs. The electrochemical properties of  $\text{Zn}\|\text{Cu}$ ,  $\text{Zn}\|\text{Zn}$ , and  $\text{Zn}\|\text{MnO}_2$  cells were systematically

studied to verify the facilitation of solvation reconfiguration and  $\text{Zn}^{2+}$  ion transportation channels in modified electrolytes on  $\text{Zn}^{2+}$  plating/stripping. According to the voltage–capacity curves of  $\text{Zn}\|\text{Cu}$  cells in  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  and  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolytes (Fig. 5a and b), there is no significant difference in the plating/stripping voltage even after 500 cycles. The maximum voltage drop in the  $\text{Zn}(\text{OTF})_2\text{-H}_2\text{O}$  electrolyte is 0.39 V (20th cycle), which is attributed to the concentration polarization of the interfacial electrolyte and the disordered deposition of  $\text{Zn}^{2+}$ . Drastic voltage fluctuations lead to the decomposition of  $\text{Zn}(\text{OTF})_2$  and dendrite growth. The maximum voltage drop in the  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolyte is only 0.069 V (200th of the cycles), thus ensuring the long-term cycling of ZIBs. The modified Aurbach method was used to analyze the  $\text{Zn}^{2+}$  desolvation kinetics.<sup>67,68</sup> The NAF-nanofilm significantly improves the  $\text{Zn}^{2+}$  plating/stripping coulombic efficiency (CE) (Fig. 5c), with the highest value of 99.86%.

Fig. 5d shows the  $\text{Zn}^{2+}$  plating/stripping CE of  $\text{Zn}\|\text{Cu}$  cells using different electrolytes at  $5 \text{ mA cm}^{-2}$ . An impressive CE of 99.71% is achieved for  $\text{Zn}\|\text{Cu}$  cells using the  $\text{Zn}(\text{OTF})_2\text{-NAF}$  electrolyte after 4500 cycles. The corresponding charge–discharge curves show more stable voltage fluctuations and gradually decreasing polarization reactions (from the 1st to 4000th cycles), proving the improvement of coulombic



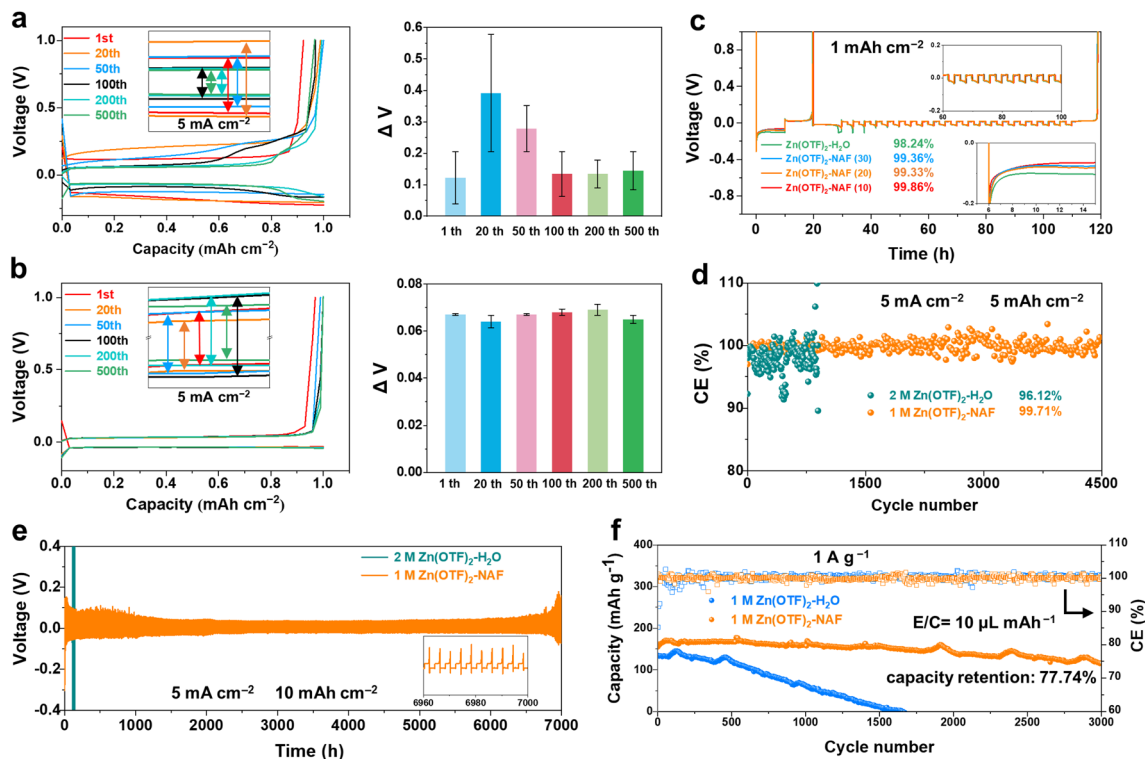


Fig. 5 Long-term deposition voltage–capacity curves and corresponding voltage fluctuation of Zn||Cu cells in (a) Zn(OTF)<sub>2</sub>-H<sub>2</sub>O and (b) Zn(OTF)<sub>2</sub>-NAF electrolytes. (c) Zn||Cu cells with different electrolytes. (d) The plating/stripping CE of Zn||Cu cells. (e) Long-term performance of Zn||Zn cells. (f) Cycling performance of Zn||MnO<sub>2</sub> cells in different electrolytes at 30 °C.

efficiency in Zn<sup>2+</sup> ion plating/deposition (Fig. S28†). For comparison, Zn||Cu cells using the Zn(OTF)<sub>2</sub>-H<sub>2</sub>O electrolyte show a CE of 96.12%. Despite the Zn<sup>2+</sup> plating/stripping in the Zn(OTF)<sub>2</sub>-MeOH electrolyte reaching 2700 h (while 280 h for the Zn(OTF)<sub>2</sub>-H<sub>2</sub>O electrolyte), the deposition overpotential of Zn<sup>2+</sup> is continuously increased from 0.3 to 0.65 V. Benefiting from the regulation of Zn<sup>2+</sup> transportation channels at the Zn anode, the NAF-nanofilm accelerates Zn<sup>2+</sup> transport in the anode/electrolyte interface. Consequently, Zn||Zn cells using the Zn(OTF)<sub>2</sub>-NAF electrolyte exhibit remarkable cycling stability with Zn<sup>2+</sup> plating/stripping for over 7000 h at 5 mA cm<sup>-2</sup> (Fig. 5e).

Besides, the cell capacity starts to decrease after 100 cycles, corresponding to the gradual depletion of Zn(OTF)<sub>2</sub> and the continuous breakage/generation of the SEI (Fig. S29†). In contrast, the Zn||MnO<sub>2</sub> cell using the Zn(OTF)<sub>2</sub>-NAF electrolyte at 30 °C demonstrates stable 3000 (dis)charging cycles at 1 A g<sup>-1</sup> with a capacity retention of 77.74% (Fig. 5f). Similar to previous studies,<sup>69</sup> the binding of MeOH to Zn<sup>2+</sup> ions improves the ionic conductivity of the Zn(OTF)<sub>2</sub>-NAF electrolyte at low temperatures. Therefore, Zn||Zn cells achieve stable plating/stripping at 1 mA cm<sup>-2</sup> for 1200 h even at -40 °C (Fig. S30†). Even at -40 °C, Zn||MnO<sub>2</sub> cells using the Zn(OTF)<sub>2</sub>-NAF electrolyte demonstrate stable 2000 (dis)charging cycles at 0.5 A g<sup>-1</sup> with a capacity retention of 66.41% (Fig. S31 and S32†). Zn(OTF)<sub>2</sub>-NAF with excellent electrochemical performance highlights its promising

application prospects in advanced ZIBs (Tables S4 and S5†), especially in harsh environments.

## Conclusion

In conclusion, Nafion as an additive is introduced into an aqueous electrolyte to construct Zn<sup>2+</sup> ion directional transmission channels for establishing an ultrastable Zn/electrolyte interface for advanced ZIBs. NAF molecules allow the *in situ* generation of a zincophilic nanofilm which serves as directional Zn<sup>2+</sup> transport channels with a more negative binding energy to induce Zn<sup>2+</sup> nucleation along the (002) crystal surface. Benefiting from the artificial ion transportation channels, the dendrite growth and anode corrosion are substantially controlled in Zn(OTF)<sub>2</sub>-NAF electrolyte. Consequently, Zn||Cu cells achieve an impressive coulombic efficiency of 99.71% after 4500 cycles, and Zn||Zn cells demonstrate stable plating/stripping for 7000 h at 5 mA cm<sup>-2</sup>. Even at -40 °C, the reversible plating/stripping of Zn||Zn cells can work over 1200 h. This work offers appealing insights into the microscopic Zn/electrolyte interfacial modulation with obviated Zn-dendrites and H<sub>2</sub>O-originated parasitic reactions for advanced ZIBs.

## Data availability

The data that support the findings of this study are available within the article and its ESI,† or from the corresponding author on reasonable request.





## Author contributions

The authors contributed to this work in the following ways: conceptualization (M. Liu, D. Zhang, Z. Song); data curation (D. Zhang); formal analysis (M. Liu, D. Zhang); funding acquisition (M. Liu, L. Gan, Y. Lv); investigation (M. Liu, D. Zhang, L. Miao); methodology (M. Liu, D. Zhang, Z. Song, L. Gan, L. Miao, Y. Lv); project administration (M. Liu); supervision (M. Liu); validation (M. Liu, L. Gan, Y. Lv); visualization (M. Liu, D. Zhang, L. Miao); writing – original draft (D. Zhang); writing – review & editing (M. Liu, D. Zhang, Z. Song).

## Conflicts of interest

The authors declare no conflict of interest.

## Acknowledgements

This work is financially supported by the National Natural Science Foundation of China (No. 22272118, 22172111, 21905207 and 22309134), the Science and Technology Commission of Shanghai Municipality, China (No. 22ZR1464100, 20ZR1460300 and 19DZ2271500), China Post-doctoral Science Foundation (2022M712402), Shanghai Rising-Star Program (23YF1449200), Zhejiang Provincial Science and Technology Project (2022C01182), and the Fundamental Research Funds for the Central Universities (22120210529 and 2023-3-YB-07).

## Notes and references

- 1 L. Cao, D. Li, T. Pollard, T. Deng, B. Zhang, C. Yang, L. Chen, J. Vatamanu, E. Hu, M. J. Hourwitz, L. Ma, M. Ding, Q. Li, S. Hou, K. Gaskell, J. T. Fourkas, X. Q. Yang, K. Xu, O. Borodin and C. Wang, *Nat. Nanotechnol.*, 2021, **16**, 902–910.
- 2 Z. Song, L. Miao, H. Duan, L. Ruhlmann, Y. Lv, D. Zhu, L. Li, L. Gan and M. Liu, *Angew. Chem., Int. Ed.*, 2022, **61**, e202208821.
- 3 N. Yao, X. Chen, Z. H. Fu and Q. Zhang, *Chem. Rev.*, 2022, **122**, 10970–11021.
- 4 Z. Song, L. Miao, L. Ruhlmann, Y. Lv, L. Li, L. Gan and M. Liu, *Angew. Chem., Int. Ed.*, 2023, **62**, e202219136.
- 5 Z. Wang, J. Huang, Z. Guo, X. Dong, Y. Liu, Y. Wang and Y. Xia, *Joule*, 2019, **3**, 1289–1300.
- 6 Z. Song, L. Miao, Y. Lv, L. Gan and M. Liu, *Angew. Chem., Int. Ed.*, 2023, **62**, e202309446.
- 7 C. Hu, Y. Qin, Z. Song, P. Liu, L. Miao, H. Duan, Y. Lv, L. Xie, M. Liu and L. Gan, *J. Colloid Interface Sci.*, 2024, **658**, 856–864.
- 8 D. Zhang, R. Gu, Y. Yang, J. Ge, J. Xu, Q. Xu, P. Shi, M. Liu, Z. Guo and Y. Min, *Angew. Chem., Int. Ed.*, 2024, e202315122.
- 9 Z. Cao, P. Zhuang, X. Zhang, M. Ye, J. Shen and P. M. Ajayan, *Adv. Energy Mater.*, 2020, **10**, 2001599.
- 10 Y. Pan, S. Liu, K. Sun, X. Chen, B. Wang, K. Wu, X. Cao, W. C. Cheong, R. Shen, A. Han, Z. Chen, L. Zheng, J. Luo, Y. Lin, Y. Liu, D. Wang, Q. Peng, Q. Zhang, C. Chen and Y. Li, *Angew. Chem., Int. Ed.*, 2018, **57**, 8614–8618.
- 11 C. C. Hou, Y. Wang, L. Zou, M. Wang, H. Liu, Z. Liu, H. F. Wang, C. Li and Q. Xu, *Adv. Mater.*, 2021, **33**, 2101698.
- 12 L. Miao, Z. Song, W. Du, X. Zheng, Y. Lv, L. Gan and M. Liu, *Mater. Chem. Front.*, 2023, **7**, 2731–2749.
- 13 P. Xiong, Y. Zhang, J. Zhang, S. H. Baek, L. Zeng, Y. Yao and H. S. Park, *EnergyChem*, 2022, **4**, 100076.
- 14 H. Dou, M. Xu, B. Wang, Z. Zhang, G. Wen, Y. Zheng, D. Luo, L. Zhao, A. Yu, L. Zhang, Z. Jiang and Z. Chen, *Chem. Soc. Rev.*, 2021, **50**, 986–1029.
- 15 P. Xiong, C. Lin, Y. Wei, J.-H. Kim, G. Jang, K. Dai, L. Zeng, S. Huang, S. J. Kwon, S. Y. Lee and H. S. Park, *ACS Energy Lett.*, 2023, **8**, 2718–2727.
- 16 Y. Zhang, Z. Song, L. Miao, Y. Lv, L. Gan and M. Liu, *Angew. Chem., Int. Ed.*, 2024, **63**, e202316835.
- 17 M. Peng, X. Tang, K. Xiao, T. Hu, K. Yuan and Y. Chen, *Angew. Chem., Int. Ed.*, 2023, **62**, e202302701.
- 18 B. Niu, Z. Li, D. Luo, X. Ma, Q. Yang, Y. E. Liu, X. Yu, X. He, Y. Qiao and X. Wang, *Energy Environ. Sci.*, 2023, **16**, 1662–1675.
- 19 Y. Wu, T. Zhang, L. Chen, Z. Zhu, L. Cheng, S. Gu, Z. Li, Z. Tong, H. Li, Y. Li, Z. Lu, W. Zhang and C. S. Lee, *Adv. Energy Mater.*, 2023, **13**, 2300719.
- 20 Q. Zhang, J. Luan, L. Fu, S. Wu, Y. Tang, X. Ji and H. Wang, *Angew. Chem., Int. Ed.*, 2019, **58**, 15841–15847.
- 21 P. Xiong, Y. Kang, N. Yao, X. Chen, H. Mao, W.-S. Jang, D. M. Halat, Z. H. Fu, M. H. Jung, H. Y. Jeong, Y. M. Kim, J. A. Reimer, Q. Zhang and H. S. Park, *ACS Energy Lett.*, 2023, **8**, 1613–1625.
- 22 Y. Wang, Q. Li, H. Hong, S. Yang, R. Zhang, X. Wang, X. Jin, B. Xiong, S. Bai and C. Zhi, *Nat. Commun.*, 2023, **14**, 3890.
- 23 Y. Cui, Q. Zhao, X. Wu, X. Chen, J. Yang, Y. Wang, R. Qin, S. Ding, Y. Song, J. Wu, K. Yang, Z. Wang, Z. Mei, Z. Song, H. Wu, Z. Jiang, G. Qian, L. Yang and F. Pan, *Angew. Chem., Int. Ed.*, 2020, **59**, 16594–16601.
- 24 H. Qiu, X. Du, J. Zhao, Y. Wang, J. Ju, Z. Chen, Z. Hu, D. Yan, X. Zhou and G. Cui, *Nat. Commun.*, 2019, **10**, 5374.
- 25 Q. Zhang, Y. Ma, Y. Lu, Y. Ni, L. Lin, Z. Hao, Z. Yan, Q. Zhao and J. Chen, *J. Am. Chem. Soc.*, 2022, **144**, 18435–18443.
- 26 Y. Xie, J. Huang, T. Kong, X. Zhou, K. Wu, X. Liu, J. Yi, L. Xing and Y. Xia, *Energy Storage Mater.*, 2023, **56**, 218–226.
- 27 J. F. Parker, J. S. Ko, D. R. Rolison and J. W. Long, *Joule*, 2018, **2**, 2519–2527.
- 28 L. Zhang, I. A. Rodríguez Pérez, H. Jiang, C. Zhang, D. P. Leonard, Q. Guo, W. Wang, S. Han, L. Wang and X. Ji, *Adv. Funct. Mater.*, 2019, **29**, 1902653.
- 29 Q. Yang, Q. Li, Z. Liu, D. Wang, Y. Guo, X. Li, Y. Tang, H. Li, B. Dong and C. Zhi, *Adv. Mater.*, 2020, **32**, 2001854.
- 30 W. Yuan, X. Nie, G. Ma, M. Liu, Y. Wang, S. Shen and N. Zhang, *Angew. Chem., Int. Ed.*, 2023, **62**, e202218386.
- 31 S. D. Pu, C. Gong, Y. T. Tang, Z. Ning, J. Liu, S. Zhang, Y. Yuan, D. Melvin, S. Yang, L. Pi, J. J. Marie, B. Hu, M. Jenkins, Z. Li, B. Liu, S. C. E. Tsang, T. J. Marrow, R. C. Reed, X. Gao, P. G. Bruce and A. W. Robertson, *Adv. Mater.*, 2022, **34**, 2202552.



- 32 J. Wang, B. Zhang, Z. Cai, R. Zhan, W. Wang, L. Fu, M. Wan, R. Xiao, Y. Ou, L. Wang, J. Jiang, Z. W. Seh, H. Li and Y. Sun, *Sci. Bull.*, 2022, **67**, 716–724.
- 33 D. Yuan, J. Zhao, H. Ren, Y. Chen, R. Chua, E. T. J. Jie, Y. Cai, E. Edison, W. Manalastas Jr, M. W. Wong and M. Srinivasan, *Angew. Chem., Int. Ed.*, 2021, **60**, 7213–7219.
- 34 M. Zhou, S. Guo, J. Li, X. Luo, Z. Liu, T. Zhang, X. Cao, M. Long, B. Lu, A. Pan, G. Fang, J. Zhou and S. Liang, *Adv. Mater.*, 2021, **33**, 2100187.
- 35 Z. Huang, Z. Li, Y. Wang, J. Cong, X. Wu, X. Song, Y. Ma, H. Xiang and Y. Huang, *ACS Energy Lett.*, 2023, **8**, 372–380.
- 36 H. Zhang, X. Gan, Z. Song and J. Zhou, *Angew. Chem., Int. Ed.*, 2023, **62**, e202217833.
- 37 L. Zhang, J. Huang, H. Guo, L. Ge, Z. Tian, M. Zhang, J. Wang, G. He, T. Liu, J. Hofkens, D. J. L. Brett and F. Lai, *Adv. Energy Mater.*, 2023, **13**, 2203790.
- 38 C. Li, R. Kingsbury, L. Zhou, A. Shyamsunder, K. A. Persson and L. F. Nazar, *ACS Energy Lett.*, 2022, **7**, 533–540.
- 39 D. Li, L. Cao, T. Deng, S. Liu and C. Wang, *Angew. Chem., Int. Ed.*, 2021, **60**, 13035–13041.
- 40 Q. Li, Y. Wang, F. Mo, D. Wang, G. Liang, Y. Zhao, Q. Yang, Z. Huang and C. Zhi, *Adv. Energy Mater.*, 2021, **11**, 2003931.
- 41 H. Tian, G. Feng, Q. Wang, Z. Li, W. Zhang, M. Lucero, Z. Feng, Z.-L. Wang, Y. Zhang, C. Zhen, M. Gu, X. Shan and Y. Yang, *Nat. Commun.*, 2022, **13**, 7922.
- 42 X. Huo, L. Xu, K. Xie, K. Zhang, J. Li, D. Wang and K. Shu, *Adv. Energy Mater.*, 2023, **13**, 2203066.
- 43 Z. Hu, F. Zhang, Y. Zhao, H. Wang, Y. Huang, F. Wu, R. Chen and L. Li, *Adv. Mater.*, 2022, **34**, 2203104.
- 44 P. X. Sun, Z. Cao, Y. X. Zeng, W. W. Xie, N. W. Li, D. Luan, S. Yang, L. Yu and X. W. Lou, *Angew. Chem., Int. Ed.*, 2022, **61**, e202115649.
- 45 J. Hao, B. Li, X. Li, X. Zeng, S. Zhang, F. Yang, S. Liu, D. Li, C. Wu and Z. Guo, *Adv. Mater.*, 2020, **32**, 2003021.
- 46 L. Yan, Y. Zhang, Z. Ni, Y. Zhang, J. Xu, T. Kong, J. Huang, W. Li, J. Ma and Y. Wang, *J. Am. Chem. Soc.*, 2021, **143**, 15369–15377.
- 47 K. Zhu, C. Guo, W. Gong, Q. Xiao, Y. Yao, K. Davey, Q. Wang, J. Mao, P. Xue and Z. Guo, *Energy Environ. Sci.*, 2023, **16**, 3612–3622.
- 48 X. Liu, F. Yang, W. Xu, Y. Zeng, J. He and X. Lu, *Adv. Sci.*, 2020, **7**, 2002173.
- 49 Y. Zeng, Z. Lai, Y. Han, H. Zhang, S. Xie and X. Lu, *Adv. Mater.*, 2018, **30**, 1802396.
- 50 R. Chen, Q. Liu, L. Xu, X. Zuo, F. Liu, J. Zhang, X. Zhou and L. Mai, *ACS Energy Lett.*, 2022, **7**, 1719–1727.
- 51 R. Kim, S. Yuk, J.-H. Lee, C. Choi, S. Kim, J. Heo and H.-T. Kim, *J. Membr. Sci.*, 2018, **564**, 852–858.
- 52 Y. Lin, Z. Mai, H. Liang, Y. Li, G. Yang and C. Wang, *Energy Environ. Sci.*, 2023, **16**, 687–697.
- 53 R. Chen, C. Zhang, J. Li, Z. Du, F. Guo, W. Zhang, Y. Dai, W. Zong, X. Gao, J. Zhu, Y. Zhao, X. Wang and G. He, *Energy Environ. Sci.*, 2023, **16**, 2540–2549.
- 54 C. Li, R. Kingsbury, A. S. Thind, A. Shyamsunder, T. T. Fister, R. F. Klie, K. A. Persson and L. F. Nazar, *Nat. Commun.*, 2023, **14**, 3067.
- 55 Y. Wang, B. Liang, J. Zhu, G. Li, Q. Li, R. Ye, J. Fan and C. Zhi, *Angew. Chem., Int. Ed.*, 2023, **62**, e202302583.
- 56 S. Carli, M. Bianchi, E. Zucchini, M. Di Lauro, M. Prato, M. Murgia, L. Fadiga and F. Biscarini, *Adv. Healthc. Mater.*, 2019, **8**, 1900765.
- 57 H. Ao, W. Zhu, M. Liu, W. Zhang, Z. Hou, X. Wu, Y. Zhu and Y. Qian, *Small Methods*, 2021, **5**, 2100418.
- 58 W. Guo, W. Zhang, Y. Si, D. Wang, Y. Fu and A. Manthiram, *Nat. Commun.*, 2021, **12**, 3031.
- 59 S. Liu, J. Vongsvivut, Y. Wang, R. Zhang, F. Yang, S. Zhang, K. Davey, J. Mao and Z. Guo, *Angew. Chem., Int. Ed.*, 2023, **62**, e202215600.
- 60 J. G. Highfield, M. H. Chen, P. T. Nguyen and Z. Chen, *Energy Environ. Sci.*, 2009, **2**, 991–1002.
- 61 G. N. Nomikos, P. Panagiotopoulou, D. I. Kondarides and X. E. Verykios, *Appl. Catal. B: Environ.*, 2014, **146**, 249–257.
- 62 C. Li, K. Domen, K. i. Maruya and T. Onishi, *J. Catal.*, 1990, **125**, 445–455.
- 63 J. Hao, L. Yuan, Y. Zhu, M. Jaroniec and S. Z. Qiao, *Adv. Mater.*, 2022, **34**, 2206963.
- 64 F. Hui and M. Lanza, *Nat. Electron.*, 2019, **2**, 221–229.
- 65 Y. Wang, S. A. Skaanvik, X. Xiong, S. Wang and M. Dong, *Matter*, 2021, **4**, 3483–3514.
- 66 P. Shi, J. Ma, M. Liu, S. Guo, Y. Huang, S. Wang, L. Zhang, L. Chen, K. Yang, X. Liu, Y. Li, X. An, D. Zhang, X. Cheng, Q. Li, W. Lv, G. Zhong, Y.-B. He and F. Kang, *Nat. Nanotechnol.*, 2023, **18**, 602–610.
- 67 D. Wang, D. Lv, H. Liu, S. Zhang, C. Wang, C. Wang, J. Yang and Y. Qian, *Angew. Chem., Int. Ed.*, 2022, **61**, e202212839.
- 68 M. H. Chung, *Electrochim. Acta*, 2000, **45**, 3959–3972.
- 69 B. D. Adams, J. Zheng, X. Ren, W. Xu and J. G. Zhang, *Adv. Energy Mater.*, 2018, **8**, 1702097.

