

Journal of Materials Chemistry A

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

ARTICLE

A One-Step Route to Solubilised, Purified or Functionalised Single-Walled Carbon Nanotubes

A. J. Clancy,^a J. Melbourne^a and M. S. P. Shaffer^{a*}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Reductive dissolution is a promising processing route for single walled carbon nanotubes (SWCNTs) that avoids the damage caused by ultrasonication and aggressive oxidation whilst simultaneously allowing access to a wealth of SWCNT functionalisation reactions. Here, reductive dissolution has been simplified to a single one-pot reaction through the use of sodium naphthalide in dimethylacetamide allowing direct synthesis of SWCNTn Na⁺ solutions. Gram quantities of SWCNTs can be dissolved at concentrations over 2 mg mL⁻¹. These reduced SWCNT solutions can easily be functionalised through the addition of alkyl halides; reducing steric bulk of the grafting moiety and increasing polarisability of the leaving group increases the extent of functionalisation. An optimised absolute sodium concentration of 25 mM is shown to be more important than carbon to metal ratio in determining the maximum degree of functionalisation. This novel dissolution system can be modified for use as a non-destructive purification route for raw SWCNT powder by adjusting the degree of charging to dissolve carbonaceous impurities, catalyst particles and defective material, before processing the remaining SWCNTs.

1. Introduction

Since their discovery, single walled carbon nanotubes (SWCNTs) have been of great interest due to their high strength,¹ stiffness, surface area, and aspect ratio, along with their interesting optoelectronic² and thermal properties.³ However, due to their high surface energy⁴ (0.5 eV nm⁻¹), as-produced SWCNTs form aligned bundles⁵ which are mechanically⁶ and electronically⁷ inferior to individualised nanotubes in most applications. Functionalisation of bundled SWCNTs generally occurs at the exposed exterior surface limiting both the total level and the uniformity of functionalisation. As-synthesised carbon nanotubes also routinely contain impurities both in the form of non-nanotube carbons (amorphous and graphitic carbon, and short defective nanotubes) and residual catalyst particles, often contained within graphitic shells and CNT caps.⁸⁻¹⁰ For these reasons, the superlative properties of SWCNTs can generally only be exploited after purification, individualisation, and stabilisation of the nanotubes in a solvent.

The most common route to dispersing SWCNT bundles uses intense sonication and stabilisation of the resulting suspensions with aqueous surfactant solutions,¹¹ amphiphilic or conjugated polymers,¹² DNA¹³ or amidic/amidinic solvents such as N-methyl pyrrolidone (NMP).¹⁴⁻¹⁶ Sonication is difficult to scale and both damages the SWCNT sp² framework and reduces aspect ratio;¹⁷ although alternative, scalable high

shear mechanical force dispersion techniques have recently been applied to carbon nanotubes, damage is still a significant issue.¹⁸ In any case, the solution formed through sonication still consists primarily of smaller bundles of nanotubes; although the individualised fraction can be separated by ultracentrifugation, it is a low yield, costly, and time consuming process. Oxidation by refluxing nanotubes in nitric acid (or other oxidising conditions) can purify the sample,¹⁹ etching away carbonaceous impurities and dissolving metal contaminants, and introducing potentially useful carboxyl groups;²⁰ however, the resultant nanotubes are heavily damaged in the process with carbons atoms removed from the framework,²¹ leading to large reductions in mechanical properties.²²

An alternative route to SWCNT dissolution involves charging of the nanotubes leading to electrostatic repulsion of the resultant nanotube anions²³ (or nanotubium cations) allowing a spontaneous route to truly individualised solutions of nanotubes without damage to the sp² carbon framework.²⁴ Addition of SWCNTs to chlorosulfonic acid²⁵ leads to spontaneous dissolution of the nanotubes²⁶ through protonation of the SWCNT sidewalls (which can be deprotonated *via* addition to water)²⁷ at very high concentration.²⁸ However, chlorosulfonic acid is difficult to handle and is incompatible with many chemical species, limiting the options for organic functionalisation. Reductive charging can be accomplished using methodologies including direct electrochemistry,²⁹ Birch reductions,³⁰ addition of group 1 organometallics, and the use of charged organic electron transfer agents.³¹ In this latter case, dried SWCNTs are initially exposed to a charging agent, typically a group 1 metal with

^a London Centre for Nanotechnology, Department of Chemistry, Imperial College London, South Kensington, SW7 2AZ, U.K

* Footnotes relating to the title and/or authors should appear here.

Electronic Supplementary Information (ESI) available: Supplementary figures. See DOI: 10.1039/x0xx00000x

either liquid ammonia or a solution of an organic single electron transport agent such as naphthalene^{32, 33} or 4,4'-di-tert-butylbiphenyl.³³ The nanotube can then be isolated by removal of the charging agent and solvent, and dissolved in one of a selection of polar aprotic solvents. It is worth noting that although widely used for this step, DMSO is thought to partially quench the nanotube, methylating the nanotubes³⁴ at high nanotube charge densities. This approach to chemical reduction is typically a time consuming process, requiring several steps followed by high vacuum and/or elevated temperatures to remove the reduction solvent prior to dissolution in a suitable reaction solvent.

Beyond simple dissolution, the raised Fermi level of reduced SWCNTs can be used to access a host of nanotube functionalisation reactions,³⁵ thought to proceed through a single electron transfer mechanism,^{35, 36} similar to the reaction of sodium naphthalide with alkyl halides; the nanotube reduces a grafting species R-X, which decomposes to an anionic leaving group X⁻ and the radical R[•] which can graft onto the SWCNT sidewall. Many compounds can be grafted allowing for a versatile array of functionalisation, including organohalides³⁷ and disulfides³⁸ for alkyl/arylation, bromine³⁹ for halogenation, carbon dioxide²¹ for carboxylation, and epoxides⁴⁰ and vinyl monomers⁴¹ for oligo/polymerisations from the SWCNT sidewall.

There is a need to simplify and improve current SWCNT processing (dissolution, functionalisation, and purification) to accelerate work in the area. Herein, a simple SWCNT reduction system is proposed that can facilitate SWCNT dissolution (Fig. 1) and non-damaging purification; the factors which govern the extent of reductive grafting are examined elucidate the mechanism and maximise the grafting density for future application.

2. Experimental

2.1. Materials.

Elicarb single walled carbon nanotubes (PR929, batch 108511/g), supplied by Thomas Swan Ltd. were dried under vacuum ($\sim 10^{-2}$ mbar) at 300 °C for 1 h and 16 h at room temperature before use. All other chemicals were purchased from Sigma Aldrich. Solvents were purchased as anhydrous grade and further dried with activated 4 Å molecular sieves for 2 days prior to use; additionally, THF and DMSO were degassed to completion *via* freeze-pump-thaw. Sodium (99.95%) was purchased as an ingot; naphthalene (99%) was dried under vacuum in the presence of P₂O₅. All work was done in a N₂ glovebox using oven dried glassware.

2.2. Procedures

Sodium naphthalide stability tests. Sodium (5 mg) and naphthalene (28 mg) were added to 5 mL of solvent and stirred with a glass stirrer bar for 24 h. For pre-prepared sodium naphthalide tests, sodium (5 mg) and naphthalene (56 mg) were added to THF (10 mL) and stirred overnight with a glass stirrer bar. Excess naphthalene was used to ensure no

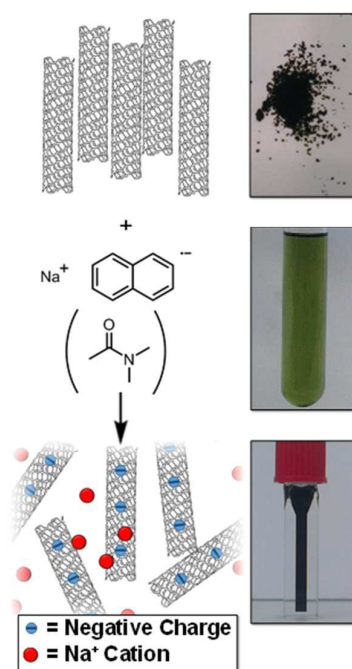


Figure 1. Schematic (left) and pictures (right) of raw SWCNT powder and NaP solution in DMAc forming a solution of nanotube

metallic sodium was present. The THF was then distilled off, the crystals were allowed to cool to RT and solvent (5 mL) was added and stirred overnight with a glass stirrer bar.

Typical SWCNT reductive dissolution. A bulk solution of sodium naphthalide in DMAc was prepared by stirring sodium (50 mg) and naphthalene (278 mg) in DMAc (50 mL) using a glass stirrer bar. For high levels of charging at high SWCNT loadings, higher concentration solutions may be necessary. Sodium naphthalide solutions were used within a week of preparation. For a 1 mg mL⁻¹ loading of SWCNTs charged to a C:Na ratio of 10:1, 19.2 mL of 1 mg_(Na) mL⁻¹ sodium naphthalide was diluted with 80.8 mL of DMAc and added to dried SWCNTs (100 mg). The mixture was stirred with a glass stirrer bar overnight before pipetting into fluorinated ethylene propylene (FEP) centrifuge tubes (Oak Ridge) with PTFE tape sealing the cap thread and centrifuging at 10,000 *g* for 30 min; solutions were then pipetted off by hand. Concentrations were measured by quenching 10 mL of solution by bubbling with dry oxygen for ~ 20 min before filtering over a tared 100 nm pore PTFE membrane and washing with copious amounts of ethanol, DI water, and acetone, ensuring the sample did not dry out between washings. The sample was then dried at 150 °C for 3 hours and weighed. A membrane subjected to the same washing procedure using 10 mL of DMAc *in lieu* of the SWCNT solution returned the tared weight (within 0.1 mg).

Alkylation of reduced SWCNTs. A solution of reduced SWCNTs (10 mg SWCNT) was diluted with DMAc to the desired concentration. Alkyl halides were dried (activated 10X molecular sieves) and degassed (if liquid, *via* freeze-pump-thaw) and added to the SWCNT solution (1 molar eq. vs. Na) then stirred overnight with a glass stirrer bar, before bubbling

with dry oxygen for ~20 min followed by filtering over a 100 nm pore PTFE membrane and washing with copious ethanol, DI water, and acetone, ensuring the sample did not dry out between washings.

Typical SWCNT purification. Premade sodium naphthalide solution in DMAc was added to SWCNTs as above, but solutions were left to stand for 48 h without stirring. The mixture was pipetted into FEP centrifuge tubes with PTFE tape sealing the cap thread and centrifuging at 10,000 *g* for 30 min; supernatant was decanted. Supernatant concentrations were measured as above. Residual purified nanotubes were exposed to a dry oxygen environment overnight and washed by stirring in ethanol, water and acetone, filtering over 100 nm PTFE membranes between steps. It should be noted that some impurities (*e.g.* residual catalyst particles) may be smaller than the membrane pore size thus the yields should be treated as a lower bound.

2.3 Measurements

UV-Vis spectra were taken with a Perkin Elmer Lambda 450 with an integration time of 0.5 s in an optical glass cuvette with a pathlength of 4 mm and screw-top lid with PTFE tape sealing the thread for air sensitive samples. When $A > 1.0$, the sample was diluted 10 x and spectra values were multiplied by 10. SEM images and EDX spectra were taken using a Leo Gemini 1525 FEGSEM at an accelerating voltage of 10 keV for SEM, and 20 keV for EDX. TEM images were taken with a JEOL 2000 with an accelerating voltage of 100 keV. Raman spectra were taken with a ISA Jobin Yvon SPEX Raman exciting with a 25 mW 532 nm laser. Statistical Raman was performed with a Renishaw inVia micro-Raman Spectrometer with 633 nm laser. TGA measurements were taken with a Perkin Elmer Pyris 1 under N_2 at 60 mL min^{-1} holding for 60 min at 100 °C before increasing the temperature at 10 °C min^{-1} to 800 °C. AFM was performed on samples drop-cast onto cleaned (H_2SO_4/H_2O_2) silicon wafers, dried, and soaked in ethanol and water. AFM micrographs were taken by tapping mode on a Digital Instruments Multimode VIII AFM with Nanoscope IV Digital Instruments AFM controller (Veeco) using Nanosensor tapping mode probes (Windsor Scientific).

3. Results and Discussion

3.1. One-step reduction and dissolution.

The key step in simplifying chemical reduction was to identify a stable reductant/solvent system using a nanotube solubilising solvent, allowing the SWCNTs to both charge and dissolve in one scalable step. Known organic solvents for nanotube include dimethyl sulfoxide (DMSO), *N,N*-dimethylformamide (DMF), and *N*-methyl-2-pyrrolidone (NMP). In addition, *N*-cyclohexyl-2-pyrrolidone (CHP), a related solvent to NMP previously identified as an optimum solvent for uncharged SWCNT dispersion via sonication,¹⁵ was tested. The reducing agent for the one-step system was selected from those proven to be successful in previous nanotube

literature. Direct (vapour) metal intercalation and Birch reductions were not considered compatible with a single-step process, whilst other organometallic reducing agents (such as BuLi) initiate undesirable side reactions, either with amide solvents, or by secondary alkylation of the nanotubes. As such, organic charge transfer agents were preferred and sodium naphthalide (NaNp) was selected as its reduction of SWCNTs is well studied,²³ and it can be easily visually identified by a characteristic green colour. A strong reducing potential⁴² is desirable to maximise the charge density on the nanotubes, as long as solvent degradation is avoided.

When either equimolar sodium and naphthalene or pre-synthesised NaNp crystals were stirred into DMSO, DMF, CHP and NMP at 1 mg(Na) mL^{-1} , the solvents turned yellow/orange and increased in viscosity. The disappearance of naphthalide's characteristic double peak (735 nm and 827 nm in THF, Fig. 2)⁴² in the UV-Vis spectra of these solutions was attributed to reaction with the solvents. The instability of NMP and CHP may relate to the opening of the strained ring. The degradation pathway of DMF in the presence of sodium metal is known⁴³ and is initiated by reduction of DMF immediately followed by removal of the formic proton to form a metal formadyl species that can further degrade to the unstable and highly basic $NaNMe_2$ which can decompose further DMF solvent molecules. A similar pathway was assumed to apply for the observed DMF degradation with NaNp (Scheme 2). It was proposed that replacement of the formic proton in DMF with a methyl group to form *N,N'*-dimethylacetamide (DMAc) would disrupt these


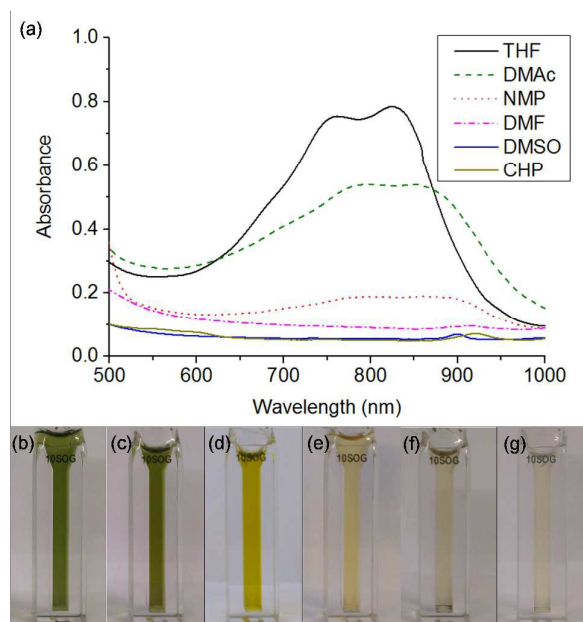


Figure 2. (a) UV-Vis spectra of equimolar sodium and naphthalene (of ~1 mg(Na) mL^{-1}) added to a selection of solvents. (b-g) Cuvettes containing the Na + Np solutions of (b) THF (c) DMAc (d) DMF (e) NMP (f) DMSO (g) CHP

pathways and prevent degradation. Addition of sodium and naphthalene to DMAc led to the formation of a green colour and full dissolution of sodium to produce 0.1 M solutions within 15 min stirring. The UV-Vis spectrum shows the expected naphthalide peaks at 757 and 850 nm; the small red-shift compared to the THF solution (22 nm) is attributed to the higher dielectric constant of DMAc, as seen for other charged organic complexes in varying solvents.⁴⁴ The extinction coefficient in DMAc appears to be intrinsically lower than in THF ($\epsilon_{761\text{nm(THF)}} = 30200 \text{ m M}^{-1}$, $\epsilon_{798\text{nm(DMAc)}} = 26200 \text{ m M}^{-1}$, ESI 1). The stability of the spectrum over time excludes any ongoing reaction between the naphthalide and the solvent; the solutions obey the Beer-Lambert law upon dilution excluding the presence of a naphthalide destructive impurity (e.g. trace water contamination). To illustrate the flexibility of this DMAc system, the stability of other known SWCNT single electron transport reducing agents, potassium naphthalide³¹ and sodium 4,4'-di-tert-butylbiphenylide,³³ was demonstrated (ESI 4).

Stirring of dried SWCNT powder (Thomas Swan Elicarb) into a solution of sodium naphthalide in DMAc (NaNp/DMAc) led to rapid dissolution with a black solution of SWCNTs forming within minutes (Scheme 1) which can be seen to be individualized by AFM (ESI 2). At a set charging ratio, here C:Na = 20:1 (Fig 3b), the concentration of nanotubide solution initially scales linearly with the loading of SWCNTs maintaining a yield between 73 – 77 %, indicating that the incomplete dissolution is not due to saturation, but is due to an inherently insoluble fraction of ~20 % wt. At higher initial loadings of SWCNTs, the concentration does not increase further, causing the yield to drop as the solution appears to saturate, here at ~2 mg mL⁻¹.

At higher degrees of charge (i.e. lower C:Na ratios), the limiting solubility occurs at higher concentrations (Fig 3a), although never at > 80 % yield for this SWCNT feedstock. At extremely high loadings (e.g. 6.5 mg mL⁻¹, ESI 3), the SWCNTs can be seen to form a gel. Increasing the degree of charge (i.e. lower C:Na ratios) with a fixed initial SWCNT loading (3.5 mg mL⁻¹) leads to an increasing yield of SWCNTs in solution as expected due to increased Coulombic repulsion; however, excessive charge is known to lead to 'salting out' effects³¹ in nanotubide solutions and polyelectrolytes in general. The concentrations here are greater than those

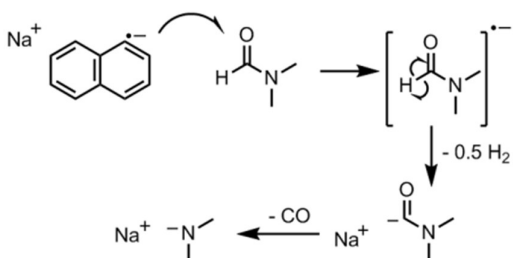

Scheme 1. Proposed decomposition of DMF in the presence of sodium naphthalide in neat solvent

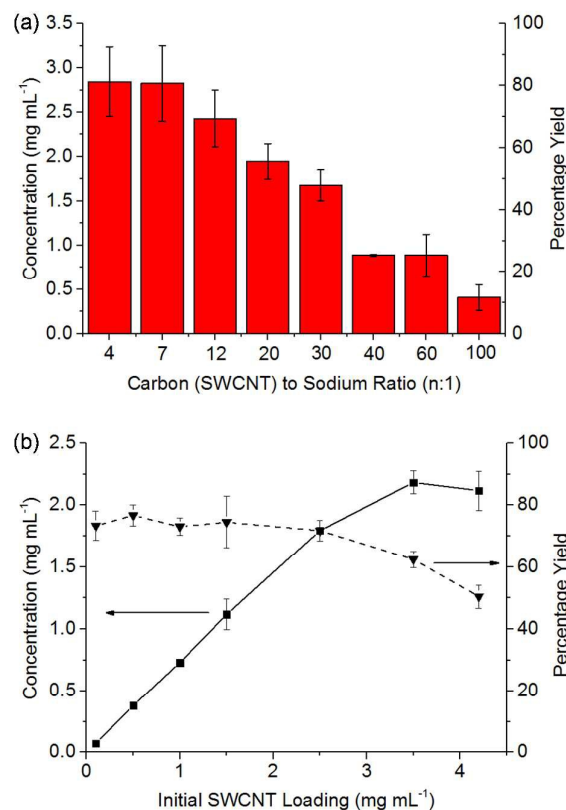


Figure 3. (a) Influence of C:Na ratio on the concentration of nanotubide solution starting with 3.5 mg mL⁻¹ loading of SWCNT. (b) The yield and concentration of nanotubide solutions against initial SWCNT loadings with 20:1 C/Na. Error bars represent standard deviations of 3 repeats.

demonstrated through NaNp charged nanotubide in DMSO (0.4 mg mL⁻¹)²³ and are on par with the sonication of predominantly bundles of SWCNTs.⁴⁵ Recent research has shown speed mixing of nanotubide salts with a solvent and crown ether leads to higher concentrations (up to 52 mg mL⁻¹), although these high concentration mixtures have not been SWCNTs(3.5 mg/mL),¹⁵ although lower than optimised sonication⁴⁶ in aqueous surfactant solution (20 mg mL⁻¹). It is worth reiterating, however that sonicated dispersions do not lead to individualized SWCNTs, instead dispersing shown to be composed of individualisation of SWCNTs⁴⁷ unlike spontaneously dispersed nanotubide solutions.²⁴

3.2. Functionalisation of reduced SWCNT solutions.

Chemical modification of SWCNTs allows adjustment of solubility,⁴⁸ wettability,⁴⁹ and introduction of new functionalities. Nanotubide solutions synthesised by reduction and dissolution with NaNp/DMAc are capable of reacting with alkyl halides to graft organic moieties, providing a quick non-damaging and simple route to grafted SWCNTs from the raw powder. The functionalisation of nanotubide solutions in DMAc was studied on a model series of alkyl halides. Firstly, the effect of varying halide leaving group was explored by reacting 20:1 charged NaNp/DMAc reduced SWCNTs with the 1-halide octanes (C₈H₁₇X; X = F, Cl, Br, I), followed by

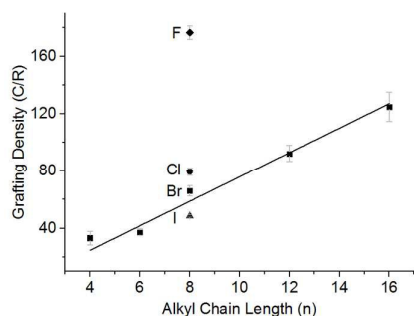


Figure 4. Grafting density of alkyl halides as a function of alkyl chain length ($C_nH_{2n+1}Br$) and halide; $C_nH_{17}X$ where $X = F$ (◆) Cl, (●), Br (■) or I (▲) for 20:1 charged SWCNTs. Line fitted to alkyl bromide series.

quenching with dry oxygen, filtering, and washing. Grafting density (alkyl groups per SWCNT carbon; lower numbers indicate higher levels of functionalisation) was calculated *via* TGA (ESI 8). There is a distinct trend of increasing halide weight increasing the level of functionalisation (Fig. 4); similar to the effect seen for functionalisation of graphite intercalation compounds (GICs),⁵⁰ which can be rationalised with the single electron transport mechanism.³⁶ The increasing polarisability (and less negative reduction potentials)⁵¹ of alkyl halides along the series $F < Cl < Br < I$ dictates the ease of radical anion formation through reduction by nanotubide, leading to a higher concentration of alkyl radicals formed for the heavier, polarisable alkyl halides with less negative reduction potentials, and a subsequently higher grafting density on the SWCNTs.

The steric bulk of the alkyl radical also affected the degree of functionalisation; as the reactivity of *n*-alkyl radicals do not vary significantly,⁵² any change in grafting density when varying alkyl length is attributed primarily to steric effects. On grafting a series of linear alkyl bromides ($C_nH_{2n+1}Br$ where $n = 4, 6, 8, 12, 16$) to 20:1 charged NaNp/DMAc reduced SWCNTs, a linear decrease in grafting can be seen with increasing alkyl length (Fig. 4). This near linear trend of alkyl chain length versus grafting ratio has also been observed before for GICs.^{50, 53}

Even with a highly effective leaving group and short chain (C_4H_9Br), the grafting density remains below the 20:1 that would correspond with 100 % utilisation of the 20:1 charge used to reduce the system. Some charge will be lost creating radicals which react to form dimers,⁵³ although previous work has demonstrated that the quantity of dimer produced is small.³⁵ An alternative limit to the reaction occurs as the nanotubide loses charge during the reaction and the Fermi level drops eventually beneath the reduction potential of the alkyl halide. Related phenomena have been demonstrated previously *via* the reactivity of analogous reduced graphene sheets with metal salts.⁵⁴

Altering the degree of charge on the nanotubide by varying the C:Na ratio also impacts the degree of grafting. At low charge ratios, there is less charge available for functionalisation and grafting levels are low; however, at high levels of charge the degree of grafting also decreases (Fig. 5).

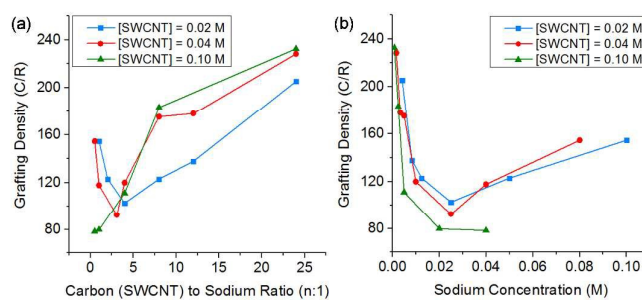


Figure 5. Grafting density of reduced SWCNTs added to 1-bromododecane versus (a) C:Na ratio, (b) sodium concentration, illustrating a shifting ideal stoichiometry but a stable sodium concentration

This behaviour can be explained by polyelectrolyte ‘salting out’ discussed earlier, leading to bundling of the SWCNTs reducing accessible surface area for grafting. The competition of these levels of charge the degree of grafting also decreases (Fig. 5). two effects (insufficient charge and salting out) leads to an ideal charge ratio for maximising the grafting of SWCNTs.

However, by changing the SWCNT loading, the ideal charge ratio shifts due to the changing concentration of sodium

This behaviour can be explained by polyelectrolyte ‘salting out’ discussed earlier, leading to bundling of the SWCNTs reducing cations. By plotting the degree of grafting as a function of sodium concentration (Fig 5b), a consistent ideal sodium concentration of ~25 mM can be identified. This effect has previously been seen for grafting of alkyl halides to exfoliated sodium graphite intercalation compounds,⁵⁰ at a lower concentration of ~10 mM. Despite the higher ionic concentration, the Debye length in the DMAc/SWCNT system is calculated to be 2.7 nm, greater than the value of 1.1 nm seen for exfoliated reduced graphite in THF, due to the higher dielectric constant of DMAc relative to THF ($\epsilon_{THF} = 7.5$, $\epsilon_{DMAc} = 37.8$); although the Debye lengths are similar (around 1-2 nm), the effect of changing geometry from planar to rod-like remains an open theoretical question.

3.3. Reductive purification of SWCNTs.

It has been previously reported that (electro)chemical reductive dissolution of a SWCNT sample proceeds *via* initial dissolution of impurities and short defective nanotubes, followed by the SWCNTs at higher reduction potentials, providing a path to SWCNT purification²⁴ During reductive purification with NaNp/DMAc, the system potential was fixed by maintaining a fixed stoichiometry of sodium to SWCNT, analogous to the potentiostatic approach used in electrochemical purification.⁵⁵ The NaNp/DMAc solution was simply poured over the dried SWCNTs; the solutions were not stirred in order to maximise any kinetic difference in dissolution of impurities and SWCNTs. Increasing charge can be seen to lead to increasing dissolution of material, though a lack of stirring led to lower levels of dissolution than the stirred counterparts (Fig 3).

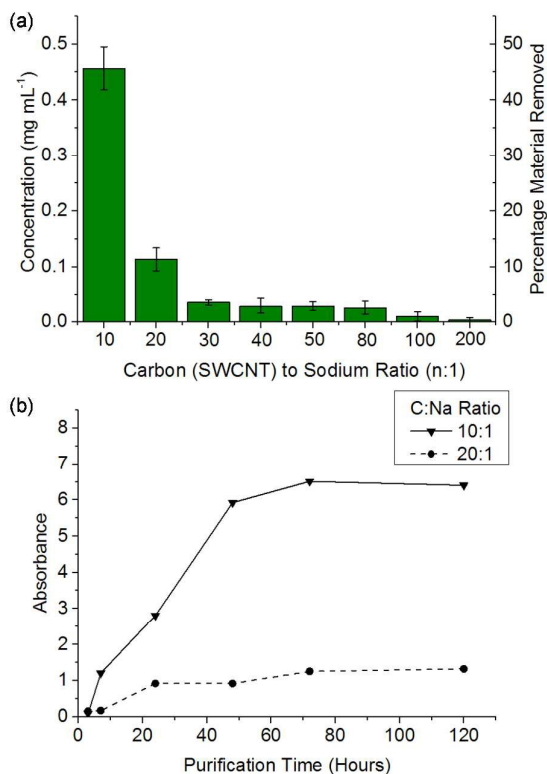


Figure 6. (a) Concentration of material dissolved versus C/Na after 48 h soaking of 1 mg mL⁻¹ SWCNT in DMAc. (b) Absorbance (660 nm) of NaNp/DMAc and SWCNTs at a given SWCNT to sodium ratio versus time.

Purification with low levels of NaNp ($\geq 30:1$ C:Na) leads to the dissolution of small levels of material (Fig 6) which TEM (ESI 5) and SEM (ESI 6) show is not CNTs; however, significant levels of carbonaceous impurities also remain in the purified fraction. Higher charge regimes increase the purity of the sample substantially, however at extreme charging regimes ($\geq 10:1$ C:Na) a significant proportion of the material is dissolved including the removal of pristine SWCNTs, illustrated by a reduction in the D/G Raman ratio of the dissolved fraction (ESI 7). Furthermore, above 20:1 C/Na, the quality of the purified sample does not increase notably with similar levels of carbonaceous impurities seen for 20:1 and 10:1 fractions, despite a further 34 wt.% of the initial SWCNT sample dissolving (Fig 6a); to prevent unnecessary loss of material during purification, an optimum C:Na ratio (around 20:1 for Elicarb SWCNTs) should be applied. The purified materials (20:1) show a decrease in average the D/G ratio (Fig 7), due to the removal of the highly defective materials; the distribution of D/G measurements around 0.05 remains similar, implying that remaining SWCNTs are undamaged. As higher concentrations and yields of nanotubide can be seen for stirred samples compared to fractions removed during the unstirred purification at similar stoichiometries, it can be assumed that the concentration values obtained from dissolution during purification are not due to saturation. The material dissolved in purification is thought to be driven

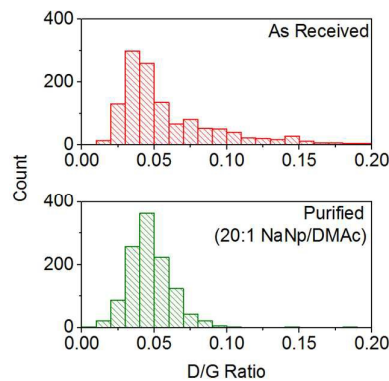


Figure 7. Distribution of D/G Raman ratios of Elicarb SWCNTs before and after Na-np purification (20:1 purification, 633 nm excitation). D/G of as received SWCNTs = 0.06 ± 0.037 , D/G of as purified SWCNTs = 0.047 ± 0.015 .

kinetically with smaller impurities able to dissolve out of the bulk, driven in part by Coulombic repulsion from the rest the sample. SWCNTs will be limited to reptation out of the network which is slow due to their high lengths (diffusion time of SWCNT reptation is inversely proportional to length cubed)⁵⁶ leading to the majority of SWCNTs being kinetically trapped in the bulk. Increasing the charge density of the system swells the network through Coulombic repulsion, allowing longer SWCNTs to escape. In addition, while the charge density of a specific carbon/inorganic species will depend on its density of states and defect concentration, the distribution of sodium between dissolved and undissolved materials (ESI 10) implies that the majority of charge remains in the undissolved material leading to the conclusion that the purification is not thermodynamically driven. By introducing stirring, the networks are physically agitated, and the concentration gradient between undissolved material surface and bulk solution reduced,⁵⁷ accelerating the reptation and dissolution of the SWCNTs and lowering the difference in timescale between impurity and SWCNT dissolution. Here, the concentration of the material dissolved will be limited by saturation or percentage of material which is intrinsically soluble, as seen for standard dissolution of SWCNTs using DMAc NaNp and stirring (Fig 3). The purification of SWCNTs benefits subsequent functionalisation; the removal of impurities increases the degree of functionalisation (ESI 11) by allowing a greater percentage of the charge added to the system to be held on the SWCNTs increasing the available charge for functionalisation, as well as removing carbonaceous debris known to hinder functionalisation.⁵⁸

4. Conclusions

In summary, a quick, simple, one-step dissolution of SWCNTs has been demonstrated through the use of DMAc as a stable solvent for both sodium naphthalide and reduced SWCNTs, enabling the synthesis of concentrated solutions of nanotubide. Additionally, the inherent scalability of the NaNp/DMAc process provides a potentially large-scale source of individualised SWCNTs, of particular use for electronic

devices and high surface area applications including electrochemical electrodes and catalyst supports. The concentrations of these solutions are notably high for individualised SWCNT solutions, particularly compared to the individualised fraction of ultracentrifuged SWCNT dispersions ($< 0.01 \text{ mg mL}^{-1}$).⁵⁹ However, the use of relatively large volumes of solvent may favour initial applications in high value/high performance applications of individualised SWNTs, for example in thin films and devices. Higher concentrations may be obtained in future if a nematic phase can be isolated and/or with the addition of complexing agents for the sodium counter-ions.⁶⁰


These solutions can be easily functionalised with a host of known reagents and the extent of grafting can be maximised by decreasing the steric bulk of the grafting species and using a leaving group with high polarisability. The extent of functionalisation can be seen to be a function of counter cation concentration with an idealized concentration of 25 mmol dm^{-3} giving a maximum grafting ratio. Additionally, modifying this method allows quick and simple access to previously demonstrated⁵⁵ reductive purification and the option to sequentially add further NaNp solution to directly dissolve the purified material. It is hoped that this work will facilitate and expand research in the versatile field of nanotubide chemistry by providing a quick and simple route to their creation using cheap, available and easy to handle reagents.

Acknowledgements

The author would like to thank Thomas Swan Ltd. and the EPSRC (EP/G007314/1, EP/L001896/1) the support of this research and S. Hodge for development of the reductive purification methodology.

1. E. Ali, D. Hadis, K. Hamzeh, K. Mohammad, Z. Nosratollah, A. Abolfazl, A. Mozghan, H. Younes and J. Sang Woo, *Nanoscale Research Letters*, 2014, DOI: 10.1186/1556-276x-9-393.
2. S. Hodge, M. Bayazit, K. Coleman and M. Shaffer, *Chemical Society reviews*, 2012, **41**, 4409-4429.
3. J. Hone, M. C. Llaguno, M. J. Biercuk, A. T. Johnson, B. Batlogg, Z. Benes and J. E. Fischer, *Appl Phys A*, 2002, **74**, 339-343.
4. L. A. Girifalco, M. Hodak and R. S. Lee, *Physical Review B*, 2000, **62**, 13104-13110.
5. T. Hasan, V. Scardaci, P. Tan and A. Rozhin..., *The Journal of ...*, 2007, DOI: 10.1021/jp0723012.
6. Yu, Files, Arepalli and Ruoff, *Physical Review Letters*, 2000, **84**, 5552-5555.
7. S. Reich, C. Thomsen and P. Ordejon, *Physical Review B*, 2002, **65**.
8. Y. Wang, H. Shan, R. Hauge, M. Pasquali and R. Smalley, *The journal of physical chemistry. B*, 2007, **111**, 1249-1252.
9. P. Tae-Jin, B. Sarbajit, H.-B. Tirandai and S. W. Stanislaus, *Journal of Materials Chemistry*, 2006, **16**.
10. G. Wei, D. Zengpei, L. He, S. Zujin, S. Hongfang and L. Yuanfang, *Carbon*, 2010, **48**.
11. T. Shastry, A. Morris-Cohen, E. Weiss and M. Hersam, *Journal of the American Chemical Society*, 2013, DOI: 10.1021/ja312235n.
12. H. Wang, J. Mei, P. Liu, K. Schmidt, G. Jimenez-Oses, S. Osuna, L. Fang, C. J. Tassone, A. P. Zoombelt, A. N. Sokolov, K. N. Houk, M. F. Toney and Z. Bao, *ACS nano*, 2013, **7**, 2659-2668.
13. M. Zheng, A. Jagota, E. D. Semke, B. A. Diner, R. S. McLean, S. R. Lustig, R. E. Richardson and N. G. Tassi, *Nature materials*, 2003, **2**, 338-342.
14. S. Bergin, Z. Sun, D. Rickard, P. Streich, J. Hamilton and J. Coleman, *ACS nano*, 2009, **3**, 2340-2350.
15. S. Bergin, Z. Sun, P. Streich and J. Hamilton..., *The Journal of ...*, 2009, DOI: 10.1021/jp908923m.
16. S. Barman, D. Pan, M. Vosgueritchian, A. Zoombelt, G. Galli and Z. Bao, *Nanotechnology*, 2012, **23**, 344011.
17. A. Lucas, C. Zakri, M. Maugey, M. Pasquali, P. Schoot and P. Poulin, *The Journal of Physical Chemistry C*, 2009, **113**, 20599-20605.
18. H. Yoon, M. Yamashita, S. Ata, D. Futaba, T. Yamada and K. Hata, *Scientific reports*, 2014, **4**, 3907.
19. S. Anil and S. C. Karl, *Carbon*, 2011, **49**.
20. N. T. Maxim, T. F. Warren, L. Giulio, E. R. Daniel and A. Sivaram, *Chemistry of Materials*, 2007, **19**.
21. B. Gebhardt, F. Hof, C. Backes, M. Müller, T. Plocke, J. Maultzsch, C. Thomsen, F. Hauke and A. Hirsch, *Journal of the American Chemical Society*, 2011, **133**, 19459-19473.
22. A. Zandiatashbar, G.-H. Lee, S. An, S. Lee, N. Mathew, M. Terrones, T. Hayashi, C. Picu, J. Hone and N. Koratkar, *Nature communications*, 2014, **5**, 3186.
23. A. Pénicaud, P. Poulin, A. Derré, E. Anglaret and P. Petit, *Journal of the American Chemical Society*, 2005, **127**, 8-9.
24. S. Fogden, C. Howard, R. Heenan, N. Skipper and M. Shaffer, *ACS nano*, 2012, **6**, 54-62.
25. A. Parra-Vasquez, N. Behabtu, M. Green, C. Pint, C. Young, J. Schmidt, E. Kesselman, A. Goyal, P. Ajayan, Y. Cohen, Y. Talmon, R. Hauge and M. Pasquali, *ACS nano*, 2010, **4**, 3969-3978.
26. A. D. Virginia, M. E. Lars, A. N. G. Parra-Vasquez, F. Hua, W. Yuhuang, P. Valentin, A. L. Jason, R. Sivarajan, K. S. Rajesh, K. Carter, W. E. Billups, W. W. Adams, H. H. Robert, E. S. Richard and P. Matteo, *Macromolecules*, 2004, **37**.
27. K. R. Pradeep, A. N. G. Parra-Vasquez, C. Jayanta, A. P. Robert, L. Feng, K. S. Anil, H. H. Robert, W. E. Billups and P. Matteo, *Journal of Nanoscience and Nanotechnology*, 2007, **7**.
28. V. Davis, A. Parra-Vasquez, M. Green, P. Rai, N. Behabtu, V. Prieto, R. Booker, J. Schmidt, E. Kesselman, W. Zhou, H. Fan, W. Adams, R. Hauge, J. Fischer, Y. Cohen, Y. Talmon, R. Smalley and M. Pasquali, *Nature nanotechnology*, 2009, **4**, 830-834.

- 29 29. S. Hodge, M. Bayazit, H. Tay and M. Shaffer, *Nature communications*, 2013, **4**, 1989.
- 30 30. K. B. Mustafa, S. Anil and S. C. Karl, *Carbon*, 2010, **48**.
- 31 31. V. Damien, D. Carlos and P. Alain, *Soft Matter*, 2011, **7**.
- 32 32. P. Alain, D. Fabienne, P. Gilles, H. Maoshuai and A. Eric, *Carbon*, 2013, DOI: 10.1016/j.carbon.2013.10.006.
- 33 33. G.-G. Ainara, O. Isabel, B. Izaskun, I. Gorka, A. Jordi, M. José Ignacio and M. A. Jesus, *Chemistry of Materials*, 2008, **20**.
- 34 34. J. Guan, Y. Martinez-Rubi, S. Dénomée, D. Ruth, C. Kingston, M. Daroszewska, M. Barnes and B. Simard, *Nanotechnology*, 2009, **20**, 245701.
- 35 35. V. Damien, R. Olivier and P. Alain, *Journal of Materials Chemistry*, 2010, **20**.
- 36 36. J. Chattopadhyay, S. Chakraborty, A. Mukherjee, R. Wang, P. S. Engel and W. E. Billups, *Journal of Physical Chemistry C*, 2007, **111**.
- 37 37. F. Liang, A. K. Sadana, A. Peera and J. Chattopadhyay..., *Nano Letters*, 2004, DOI: 10.1021/nl049428c.
- 38 38. Z. Syrgiannis, L. V. Parola and C. Hadad, *Angewandte Chemie ...*, 2013, DOI: 10.1002/anie.201301617.
- 39 39. F. Hof, F. Hauke and A. Hirsch, *Chemical Communications*, 2014, **50**, 6582-6584.
- 40 40. Y. Martinez-Rubi, B. Ashrafi, J. Guan, C. Kingston, A. Johnston, B. Simard, V. Mirjalili, P. Hubert, L. Deng and R. J. Young, *ACS applied materials & interfaces*, 2011, **3**, 2309-2317.
- 41 41. L. Feng, M. B. Jonathan, K. Kazufumi, K. S. Anil, I. V.-C. Yadira, M. T. James and W. E. Billups, *Chemistry of Materials*, 2006, **18**.
- 42 42. N. Connelly and W. Geiger, *Chem. Rev.*, 1996, **96**, 877-910.
- 43 43. B. A. R. Paul, R. Kapoor, *Indian Journal of Chemistry*, 1975, **13**, 1338.
- 44 44. N. Sarmah, P. K. Bhattacharyya and K. K. Bania, *The Journal of Physical Chemistry A*, 2014, **118**, 3760-3774.
- 45 45. N. Tummala and A. Striolo, *ACS nano*, 2009, **3**, 595-602.
- 46 46. M. F. Islam, E. Rojas, D. M. Bergey, A. T. Johnson and A. G. Yodh, *Nano Letters*, 2003, **3**.
- 47 47. C. Jiang, A. Saha, C. C. Young, D. P. Hashim, C. E. Ramirez, P. M. Ajayan, M. Pasquali and A. A. Martí, *ACS nano*, 2014, **8**, 9107-9112.
- 48 48. R. Chadwick, U. Khan, J. Coleman and A. Adronov, *Small (Weinheim an der Bergstrasse, Germany)*, 2013, **9**, 552-560.
- 49 49. Y. Martinez-Rubi, B. Ashrafi, J. Guan, C. Kingston, A. Johnston, B. Simard, V. Mirjalili, P. Hubert, L. Deng and R. Young, *ACS Appl. Mat. Interfac.*, 2011, **3**, 2309-2317.
- 50 50. T. Morishita, A. J. Clancy and M. S. P. Shaffer, *Journal of Materials Chemistry A*, 2014, **2**, 15022-15028.
- 51 51. A. A. Isse, C. Lin, M. L. Coote and A. Gennaro, *The Journal of Physical Chemistry B*, 2010, **115**, 678-684.
- 52 52. D. V. Avila, K. U. Ingold, J. Luszytk, W. R. Dolbier, H. Q. Pan and M. Muir, *Journal of the American Chemical Society*, 1994, **116**, 99-104.
- 53 53. G. D. Sargent and A. L. Glenn, *Journal of the American Chemical Society*, 1968, DOI: 10.1021/ja01027a068.
- 54 54. S. A. Hodge, H. H. Tay, D. B. Anthony, R. Menzel, D. J. Buckley, P. L. Cullen, N. T. Skipper, C. A. Howard and M. S. P. Shaffer, *Faraday Discussions*, 2014, DOI: 10.1039/c4fd00043a.
- 55 55. S. Hodge, S. Fogden, C. Howard, N. Skipper and M. Shaffer, *ACS nano*, 2013, **7**, 1769-1778.
- 56 56. N. Fakhri, MacKintosh, F.C., Lounis, B., Cognet, L., Pasquali, M., *Science (New York, N.Y.)*, 2010, **330**, 1804-1807.
- 57 57. T. Twardowski, *Introduction to Nanocomposite Materials* DEStech Publications Inc, 2007.
- 58 58. L. Shao, G. Tobias, C. G. Salzmanna, B. Ballesteros, S. Y. Hong, A. Crossley, B. G. Davis and M. L. Green, *Chemical communications (Cambridge, England)*, 2007, DOI: 10.1039/b712614j, 5090-5092.
- 59 59. S. Giordani, S. D. Bergin, V. Nicolosi, S. Lebedkin, M. M. Kappes, W. J. Blau and J. N. Coleman, *The journal of physical chemistry. B*, 2006, **110**, 15708-15718.
- 60 60. C. Jiang, A. Saha, C. Xiang, C. Young, J. Tour, M. Pasquali and A. Martí, *ACS nano*, 2013, **7**.

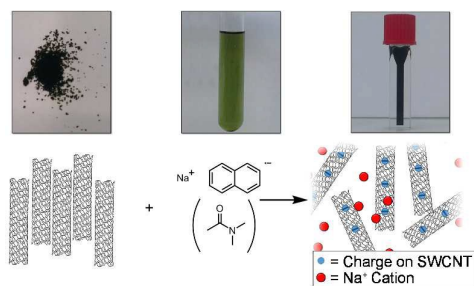

The use of N,N-dimethylformamide as a solvent for carbon nanotube reduction and dissolution allows simple and effective dissolution and purification.