



Cite this: *Nanoscale Adv.*, 2021, 3, 5722

## Functionalized carbon nanotubes: synthesis, properties and applications in water purification, drug delivery, and material and biomedical sciences

Rama Dubey, \* Dhiraj Dutta, Arpan Sarkar and Pronobesh Chattopadhyay 

Carbon nanotubes (CNTs) are considered as one of the ideal materials due to their high surface area, high aspect ratio, and impressive material properties, such as mechanical strength, and thermal and electrical conductivity, for the manufacture of next generation composite materials. In spite of the mentioned attractive features, they tend to agglomerate due to their inherent chemical structure which limits their application. Surface modification is required to overcome the agglomeration and increase their dispersability leading to enhanced interactions of the functionalized CNTs with matrix materials/polymer matrices. Recent developments concerning reliable methods for the functionalization of carbon nanotubes offer an additional thrust towards extending their application areas. By chemical functionalization, organic functional groups are generated/attached to the surfaces as well as the tip of CNTs which opens up the possibilities for tailoring the properties of nanotubes and extending their application areas. Different research efforts have been devoted towards both covalent and non-covalent functionalization for different applications. Functionalized CNTs have been used successfully for the development of high quality nanocomposites, finding wide application as chemical and biological sensors, in optoelectronics and catalysis. Non covalently functionalized carbon nanotubes have been used as a substrate for the immobilization of a large variety of biomolecules to impart specific recognition properties for the development of miniaturized biosensors as well as designing of novel bioactive nanomaterials. Functionalized CNTs have also been demonstrated as one of the promising nanomaterials for the decontamination of water due to their high adsorption capacity and specificity for various contaminants. Specifically modified CNTs have been utilized for bone tissue engineering and as a novel and versatile drug delivery vehicle. This review article discusses in short the synthesis, properties and applications of CNTs. This includes the need for functionalization of CNTs, methods and types of functionalization, and properties of functionalized CNTs and their applications especially with respect to material and biomedical sciences, water purification, and drug delivery systems.

Received 21st April 2021  
Accepted 8th August 2021

DOI: 10.1039/d1na00293g

rsc.li/nanoscale-advances

Defence Research Laboratory, Post Bag No. 2, Tezpur 784001, Assam, India,  
+91-3712-258508, +91-3712-258836, +91-3712-258534. E-mail: ramadubey@drdo.  
drdo.in



Rama Dubey obtained her PhD from Kanpur University in 2000. She was deputed to Penn State University and Arkansas University, USA in the year 2002 and 2007. Currently she is heading a team of scientists at the Defence Research Laboratory, DRDO, Tezpur, India. Her research areas are engineering and conducting polymers, smart technologies in the field of water purification, fuel and lubricants

and microwave absorption.



Dhiraj Dutta graduated in 2005 from Tezpur Central University. He is a PhD student at NIT Nagaland. He joined DRDO as a scientist in 2008. His primary interests are development of technical materials for specific applications including aero-grade materials with extremely low density.



# 1. Introduction

Since their discovery by Iijima<sup>1</sup> in 1991, carbon nanotubes (CNTs) have attracted considerable attention in applied research. There are mainly two types of carbon nanotubes: (i) single walled nanotubes (SWCNTs) and (ii) multiwalled nanotubes (MWCNTs). Both the types have rolled-up graphene sheets forming nanotube cylinders. The wall of nanotubes is made up of carbon hexagons and the tubular curved ends have some carbon pentagons. The salient features of both the types of carbon nanotubes are given in Table 1.

## 1.1 Synthesis of carbon nanotubes

Several methods have been reported for the synthesis of CNTs, but the most common methods are arc-discharge,<sup>2-7</sup> laser ablation<sup>8,9</sup> and chemical vapor deposition (CVD).<sup>10-16</sup> A comparative description of these three methods is given in Table 2. In addition to these, a few less frequently used approaches for synthesizing nanotubes are the gas phase catalytic process (HiPCO),<sup>17</sup> flame synthesis,<sup>18</sup> core shell polymer microsphere method,<sup>19</sup> aerosol precursor method,<sup>20</sup> arc water process,<sup>21</sup> low temperature route,<sup>22</sup> plasma method,<sup>23</sup> fluidized bed method<sup>24</sup> and nebulized spray process.<sup>25</sup>

## 1.2 Impressive properties of carbon nanotubes

CNTs have many magnificent properties that have motivated researchers of many disciplines to conduct intensive studies. Impressive properties in various aspects *i.e.* mechanical, electrical, thermal, chemical and biological are presented briefly in this section. Besides them, the small size of nanotubes which leads to many unique advantages will also be discussed.

**1.2.1 Mechanical properties.** CNTs possess high stiffness and axial strength as a result of carbon-carbon sp<sup>2</sup> bonding.<sup>26</sup> They are the stiffest known fiber, with a measured Young's modulus of 1.4 TPa.<sup>27</sup> Their elongation to failure is 20–30%, which combined with the stiffness projects a tensile strength above 100 GPa, the highest known so far. For example the Young's modulus of high strength steel is around 200 GPa, and its tensile strength is 1–2 GPa.<sup>28</sup>

**1.2.2 Electrical properties.** The unique electrical properties of CNTs are derived from their 1D characteristics and the peculiar electronic structure of graphite. They possess extremely low electrical resistance. In addition, they show the highest current density of any known material measured, as high as 10<sup>9</sup> A cm<sup>-2</sup>.<sup>29,30</sup> They have shown to be superconducting even at low temperatures. These unique electrical properties are utilized for fabricating field emission displays (FEDs) as well as constructing electronic computer circuits entirely out of carbon nanotubes.

**1.2.3 Thermal, chemical and biological properties.** Before CNTs, diamond was known to be the best thermal conductor. CNTs have now shown to have a thermal conductivity at least twice that of diamond.<sup>31</sup> They are chemically inert, especially when no defects are present. This makes them chemically stable and biologically compatible. Besides being chemically stable, they have a large surface to volume ratio and hence are becoming an interesting material for hydrogen storage. In terms of biological applications, SWCNTs have been used as drug delivery vehicles to bring chemicals into cells.<sup>32</sup>

**1.2.4 Small size.** The biggest advantage of CNTs is their small diameter due to which they have been attached onto normal AFM tips in order to improve their resolving capability. The small size of SWCNTs makes it easier to study chemical bindings between only one pair of receptor/target. Another application utilizing the small size of SWCNTs is as electron emitters. This kind of emitter can be used to extract electrons to generate light, either visible (TV) or X-ray (portable and high resolution X-ray machine).<sup>33</sup>

## 1.3 Applications of CNTs

Among the plethora of applications for CNTs, polymer composites, field effect transistors, field emission displays and hydrogen storage appear to be the most promising areas. For example, CNTs have been considered to be novel components for molecular electronics and for integration into conventional circuits.<sup>34</sup> CNT polymer composites are expected to be tougher and more scratch resistant than other materials.<sup>35</sup> Recently CNTs have been used as field emission electron sources.<sup>36</sup> This technology finds applications in the construction of flat panel



Arpan Sarkar completed his BSc with Chemistry honors from Calcutta University, Kolkata, West Bengal, India in 2009. Since, 2016 he has been working at the Defence Research Laboratory, Tezpur, Assam, India. He extensively surveyed the soil and water of the Eastern Himalaya region for several anthropogenic and geogenic factors and their impact on the environment. He is now involved in developing

several water purification techniques.



Pronobesh Chattopadhyay, PhD, FNASc, is currently working as Scientist and Head, Pharmaceutical Technology Division, Defence Research Laboratory, Tezpur, Assam. He has 10 patents and more than 135 publications in reputed journals, 10 monographs and 4 book chapters.



Table 1 Salient features of SWCNTs and MWCNTs

S. no.	SWCNTs	MWCNTs
1	Single layer of graphene having a diameter of 0.4 to 3.0 nm	Multiple layer (2–50) of graphene having a diameter 1.4 to 100 nm (15–55 nm preferred)
2	Catalyst is required for synthesis	Can be produced without a catalyst
3	Bulk synthesis difficult due to requirement of proper control over growth and atmospheric conditions	Bulk synthesis is easy
4	Purity is poor	Purity is high
5	Functionalization sometimes results in defect generation	Chances of defect generation during functionalization are comparatively less
6	Characterization and evaluation is easy	It is a very complex structure
7	Easily twistable and pliable	Can't be easily twisted

displays and X-rays to microwave generators.<sup>37</sup> Finally, storage of hydrogen on CNTs represents a great development in the field of fuel cells and a milestone towards energy clean systems.<sup>38,39</sup>

#### 1.4 Disadvantages of CNTs

In spite of excellent properties and widespread applications, the lack of solubility in aqueous and organic media has been a major technological barrier for CNTs. This is due to their

stable structure having pure carbon element. In addition, they have very high long range van der Waals forces of attraction due to which they have a tendency to aggregate together and it becomes very difficult to disperse them.<sup>40,41</sup> Thus the poor processability due to their insoluble and intractable nature has hindered their use in many applications. To overcome this problem of poor processability and in order to take full advantage of the properties of CNTs, functionalization and

Table 2 Comparison of main synthesis methods of carbon nanotubes

Method/requirements	CVD	Laser ablation	Arc discharge
Raw materials & availability	Fossil based & botanical hydrocarbon, abundantly available	Graphite, difficult to get	Pure graphite, difficult to get
Nature of process & description	Continuous, substrate placed in an oven, and heated to high temperature followed by slow addition of carbon bearing gas such as methane. Gas decomposes to liberate carbon atoms which combine to form nanotubes	Batch intense laser pulse used to blast graphite to generate carbon gas to form CNTs, and different conditions were tried to get optimum which produces a sufficient amount of SWCNTs	Batch two graphite rods placed a few millimeters apart and connected to a power supply. At 100 amps carbon vaporizes and forms hot plasma
Process condition	High temperatures within 500 to 1000 °C at atmospheric pressure	Argon or nitrogen gas at 500 Torr	Low-pressure inert gas (helium)
Production cost	Low	High	High
Post treatment	Not required	Required	Required
Yield	High 20–100%	Moderate 70% max	Good 30–90% max
SWCNT	Long tubes with diameters ranging from 0.6 to 4 nm	Long bundles of tubes with length 5–20 microns, and individual diameter from 1–2 nm	Short tubes having diameters in range 0.6–1.4 nm
MWCNT	Long tubes with the diameter in the range of 10 to 240 nm	MWNT synthesis is possible but it is too expensive	Short tubes with inner diameter 1–3 nm and the outer diameter approximately 10 nm
Purity	High	High	High
Production rate	High	Low	Low
Energy requirement	Moderate	High	High
Reactor design	Easy	Difficult	Difficult
Advantages	Easy to scale up, simple process, long length SWCNTs with a controllable diameter and good purity	Good quality SWNTs with high yield and narrow distribution compared to arc discharge	Less expensive with open air synthesis. Can easily produce SWNT & MWNTs. SWNT with few structural defects & MWNTs even without a catalyst
Disadvantages	Synthesized CNTs are usually with defects	Costly technique since it requires expensive lasers and high-power, limited to lab scale	Extensive purification required since nanotubes are short, tangled with random sizes and directions
References	10–16	8 and 9	2–7



Table 3 Effect of CNTs functionalization on properties


Functionalization method	Property enhancement	References
Fluorination	Enhanced solubility in organic solvents	56 and 57
1,3-Dipolar cycloaddition	Enhanced solubility in aqueous & organic solvents	62 and 63
Aryl diazonium salt reduction	Enhanced solubility in organic solvents	64 and 65
Reactive species functionalization	Further derivative functionalization	66–68
Electrophilic addition	Further derivative functionalization	69
Metal-containing molecular complex formation	Enhanced solubility & stability in organic solvents	70 and 71
Carboxylation	Further derivatization, use as molecular linker to interconnect nanotubes	74–76
Nanoparticles deposition	Soluble in water & able to trap water soluble metal ions	88–99
Surfactant functionalization	Enhanced dispersion	102–113
Polymer wrapping	Reversibly solubilized in water stable dispersion in water and organic solvents	115–121
Polymer absorption	Enhanced anchoring ability for proteins and small biomolecules, enhanced dispersion in organic solvents	122–124
Polymer encapsulation	Enhance dispersion of CNTs in a wide variety of polar and non polar solvents and polymer matrices	125–129
Metal deposition	Metal nanotube supported metal nanowire structures	130–134

solubilization of CNTs have received much recent attention. This helps to extend their application areas immensely.

### 1.5 Functionalization of CNTs and offered advantages

Functionalization is the generation of functional groups on the surfaces of CNTs. These functional groups help in decreasing

the long range van der Waals forces of attraction and increase the CNTs-matrix/solvent interaction and give rise to a homogeneous dispersion or result in solubilization of CNTs.<sup>42,43</sup> The effect of functionalization of CNTs on properties is given in Table 3. Thus functionalization enhances the reactivity, improves the solubility and provides an avenue for further chemical modification of CNTs such as ion adsorption, metal

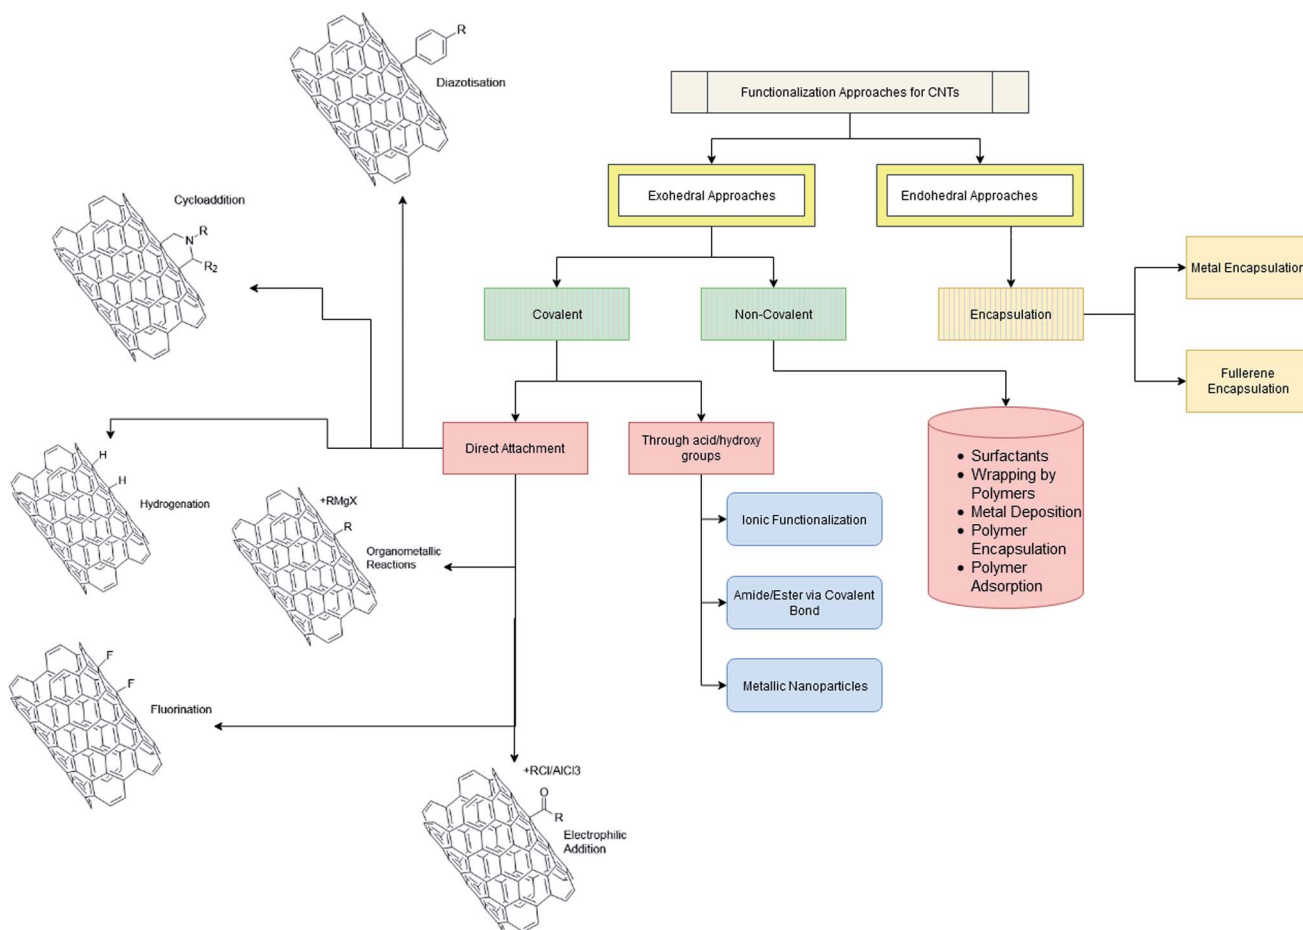

Scheme 1 Functionalization approaches for CNTs.



Table 4 Advantages and disadvantages of various methods of CNT functionalization

Methods for CNT functionalization	Advantages	Disadvantages	References
Exohedral	<ul style="list-style-type: none"> <li>• Does not disrupt the main structure of CNTs</li> <li>• Properties of both CNTs and functional group achieved</li> </ul>	<ul style="list-style-type: none"> <li>• Properties are specific to the nature of functional groups attached</li> </ul>	
Covalent	<ul style="list-style-type: none"> <li>• Covalent bonds act as substitution sites for functionalization</li> <li>• Secondary substitution reactions possible</li> <li>• Functionalization leads to enhanced solubility in water and organic solvents</li> <li>• Hydrophilic groups introduced onto the CNT surface render them more biocompatible and biodegradable</li> </ul>	<ul style="list-style-type: none"> <li>• Change of hybridization from <math>sp^2</math> to <math>sp^3</math> and loss of the p-conjugation system on the graphene layer</li> <li>• This results in quenching of the tube emission</li> <li>• Sometimes CNTs get oxidatively consumed in the process</li> </ul>	56–99
Non covalent	<ul style="list-style-type: none"> <li>• Possibility of adsorbing various groups on CNT surface without disturbing the <math>\pi</math> system of the graphene sheets</li> <li>• Hydrophobic part of the adsorbed molecules attaches with nanotube sidewalls through van der Waals, <math>\pi</math>-<math>\pi</math>, CH-<math>\pi</math> and other interactions, whereas aqueous solubility is provided by the hydrophilic part of the molecules</li> <li>• Aggregation prevented by coulombic repulsion forces between modified CNTs</li> <li>• Polymer encapsulated CNTs could be well dispersed in polymer matrices and solvents</li> <li>• NTs serve as an electrodeposition template and subsequently as a wire to electrically connect the deposited Au, Pt and Pd nanoparticles resulting in metal nanotube supported metal nanowire structures</li> <li>• Non covalent strategy to attach carboxylic functional groups through p-p stacking interactions, thereby creating stable aqueous dispersions and limiting cytotoxicity</li> </ul>	<ul style="list-style-type: none"> <li>• Stability of dispersions also depends on the nature and concentration of surfactants</li> <li>• Polymer wrapping over CNT surface is solvent dependent</li> </ul>	100–134
Endohedral	<ul style="list-style-type: none"> <li>• Buckytubes constitute smart carrier systems which may be filled with tailored materials to address specific demands</li> <li>• CNTs can be filled with anticancer antimalarial drugs</li> <li>• Sensitive biological compounds with a low melting point or high decomposition rate can be easily dissolved and introduced into the CNTs, which would otherwise be impossible through a physical route</li> <li>• MWNTs allow for prolonged release of the encapsulated drug, thereby increasing its anticancer efficacy</li> </ul>	<ul style="list-style-type: none"> <li>• This strategy requires CNTs to be opened, usually under aggressive conditions, which may lead to damaging of the outer wall or surface functionalization</li> <li>• Filling yield tends to be rather low (scarcely above 20%) and dramatically reduced with a decrease in CNT diameter, which makes the task rather difficult in the case of SWNTs and DWNTs</li> </ul>	135–157



deposition, grafting reactions *etc.* In addition the functional groups can also serve as anchor groups for joining two moieties and further derivatization by chemical reactions with other functional groups. Taking the advantages offered by functionalization of CNTs into account, a lot of modeling studies have been carried out to predict the properties of functionalized CNTs as well as their impact on other biomolecules.<sup>44–46</sup>

In this review, we have focused on different functionalization approaches for the synthesis of functionalized CNTs (f-CNTs), which are the primary prerequisite for application of CNTs in any area. Both covalent and non-covalent approaches for functionalization have been discussed in detail. The advantages and applications of f-CNTs have also been discussed with special emphasis on their application in the area of material and biomedical sciences, water purification, and drug delivery systems. Although different reviews on functionalization of CNTs and their application in the field of biomedical science, drug delivery, water treatment *etc.* have been published in the literature,<sup>47–55</sup> there is a need for a comprehensive account encompassing different application areas together which has been incorporated in this review. The goal is to offer a brief and valuable description to the reader about the key functionalization strategies developed in this field along with their potential applications in the areas of human concern. At the end, future recommendations for this exciting research area have also been provided.

## 2. Methods of functionalization

There are many well reported methods of functionalization as shown in Scheme 1. Broadly they can be classified as either exohedral or endohedral, depending on whether the modification is being done on the outside or inside walls of the CNTs. The exohedral functionalization is further subdivided into two categories: (a) covalent functionalization and (b) non-covalent functionalization. Table 4 shows the advantages and disadvantages of various functionalization methods which are discussed below.

### 2.1 Exohedral functionalization

**2.1.1 Covalent functionalization.** Covalent functionalization can roughly be divided into two categories, *i.e.* direct


attachment of functional groups to the graphitic surface such as fluorination, hydrogenation, 1,3 dipolar addition *etc.* or the use of nanotube bound carboxylic or hydroxyl functional groups for further derivatization (amidation or esterification) and chemical reactions as discussed below.

#### 2.1.1.1 Covalent functionalization by direct attachment of functional groups

(i) *Fluorination.* Fluorination of CNTs was developed by Margrave and coworkers.<sup>56</sup> Fluorination is generally carried out by treatment with molecular fluorine at temperatures between 150 and 600 °C. Depending on the reaction temperature, different degrees of fluorination can be accomplished. This method gives heavily functionalized CNTs with increased solubility in organic solvents such as alcohols.<sup>57</sup> The covalent bond formation with fluorine has been confirmed by IR spectroscopy, through the C–F valence vibration at 1220–1250 cm<sup>-1</sup>. Fluorination drastically changes the electronic properties of CNTs making them insulators when fluorination was carried out above 250 °C. However, treatment of such derivatized nanotubes with hydrazine results in defunctionalization, such that intact CNTs can be recovered. In addition, F atoms could be displaced by various nucleophiles such as organolithium and Grignard reagents to give nanotubes functionalized with organic moieties,<sup>58</sup> leading to much better dissolution properties.<sup>59</sup>

(ii) *Hydrogenation.* Pekker and coworkers reported the hydrogenation of CNTs *via* birch reduction in ammonia.<sup>60</sup> Later Han *et al.* used a gas phase technique for CNT functionalization with atomic hydrogen.<sup>61</sup> This technique proved to be useful due to its clean and low temperature process in comparison to wet chemical methods which result in the change of physical and chemical properties of CNTs. This approach used a glow discharge to generate the necessary precursors and is suitable for attaching a wide variety of chemical groups to CNTs. The functionalization was carried out with atomic hydrogen. FTIR spectroscopy showed the presence of bands at 1370 and 1457 cm<sup>-1</sup> that are due to the bending mode of C–H vibrations in SWCNTs based on functionalization with a H atom.

(iii) *1,3-Dipolar cycloadditions.* Prato and coworkers reported 1,3-dipolar cycloaddition<sup>62,63</sup> of azomethine ylides (generated by condensation of substituted  $\alpha$ -amino acids and an aldehyde as shown in Fig. 1) for functionalization of both single walled (SW)

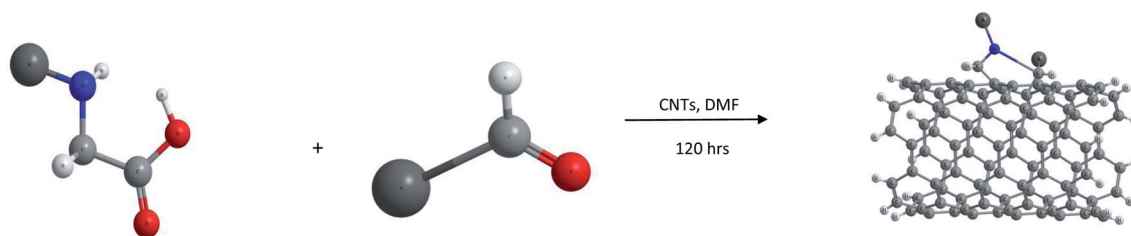

Where, R<sub>1</sub>/R<sub>2</sub> = Alkyl or Aryl Group

Fig. 1 Cycloaddition reactions of CNTs, where R<sub>1</sub>/R<sub>2</sub> = alkyl or aryl group.



as well as MWCNTs. This type of functionalization leads to a very high level of solubility of the resulting products in water as well as organic solvents such as chloroform, acetone, methanol *etc.*

The main advantage of this reaction is the easy attachment of pyrrolidine rings substituted with chemical functionalities to the side walls of the CNTs which leads to the construction of novel materials with diverse applications. Thus functionalized aldehydes can lead to 2-substituted pyrrolidine moieties located on the side walls of CNTs, while modified  $\alpha$ -amino acids could also lead to numerous diverse functionalized materials.

(iv) *Functionalization by reduction of aryl diazonium salts.* Aryl diazonium salts are known to react with olefins resulting in arylation of aromatic compounds. Hence SWCNTs have also been functionalized with aryl moieties by the reduction of a variety of substituted aryl diazonium salts either electrochemically<sup>64</sup> or under normal room temperature conditions<sup>65</sup> as shown in Fig. 2. It was found that CNTs derivatized with a 4-*tert*-butylbenzene moiety possess much improved solubility in organic solvents. However the functionalizing moieties can be removed by heating in an argon atmosphere.

As described by J. M. Tour *et al.*<sup>64,65</sup> both direct treatment of SWCNTs with aryl diazonium tetrafluoroborate salts in solution and *in situ* generation of diazonium with an alkyl nitrite are effective means of functionalization. In some cases direct treatment with preformed diazonium salts is observed to be effective at moderate or even room temperature. However the *in situ* generation of diazonium species is advantageous since it avoids the necessity of isolating and storing unstable and light sensitive aryl diazonium salts.


(v) *Reactive species functionalization.* This type of functionalization was reported by M. Holzinger *et al.*<sup>66,67</sup> and is achieved by

directly reacting CNTs with highly reactive groups such as nitrenes, carbenes, radicals *etc.*<sup>68</sup> as shown in Fig. 3 and 4. For example the thermal reaction of alkyl azidoformates leads to N<sub>2</sub> extrusion and alkoxy-carbonylaziridino derivatized CNTs, which are soluble in organic solvents such as DMSO.

Stable solutions of functionalized SWCNTs are also formed from the addition of nucleophilic carbenes. Deprotonation of the dipyrindyl imidazolium system leads to the generation of dipyrindyl imidazolidene resulting in carbene addition. They react with the electrophilic  $\pi$  system of CNTs to give zwitterionic 1 : 1 adducts rather than cyclopropane systems because of the special stability of the resultant aromatic 14  $\pi$  perimeter. Because of its high nucleophilicity, side wall functionalization of SWCNTs takes place by a nucleophilic polyaddition reaction. Thus, in this case no cyclopropanation occurs; rather each added group is bound through just one covalent bond to the tube and is positively charged due to the transfer of one negative charge per addend to the nanotube framework. The high solubility of carbene adducts is due to mutual electrostatic repulsion of the tubes.

Functionalization of SWCNTs with radicals was also carried out by photoinduced addition of perfluorinated alkyl radicals as shown in Fig. 4. This was conducted by irradiating a solution of hepta-decafluorooctyl iodide with a mercury lamp. However, the fluoroalkyl substituted NTs did not show any improvement in solubility compared to raw SWCNTs.

(vi) *Electrophilic addition.* An electrophilic addition to SWCNTs (prepared by a gas phase catalytic method) was reported by N. Tagmatarchis *et al.*<sup>69</sup> Upon a mechanochemical reaction in the presence of a Lewis acid, such as aluminum trichloride (AlCl<sub>3</sub>), a molecule of chloroform was found to be added to the side walls of CNTs. It was also possible to exchange

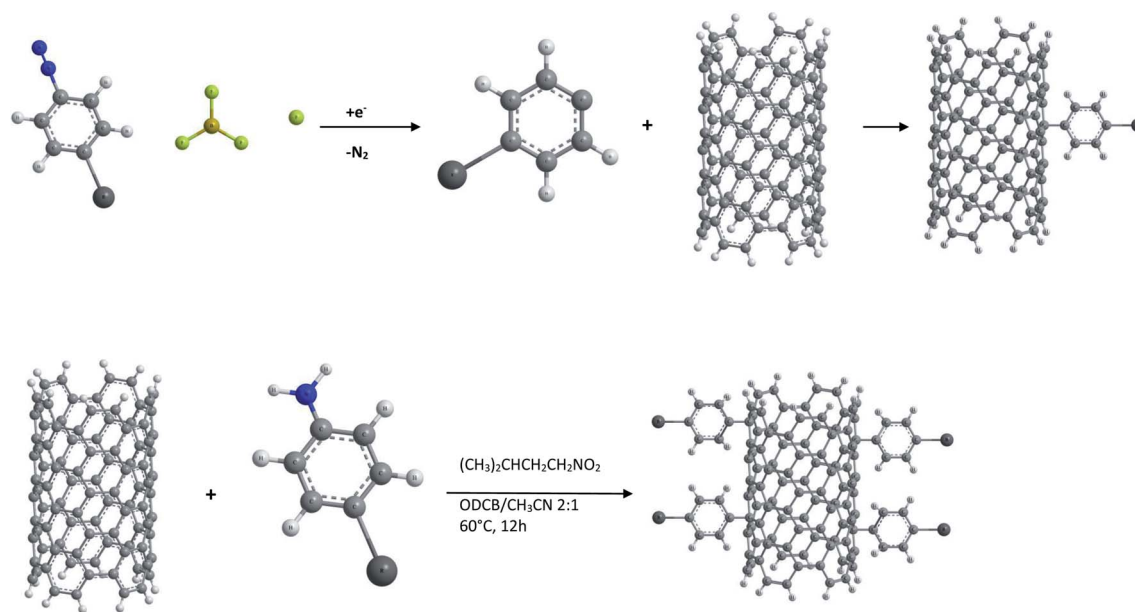

Where, R = Cl, NO<sub>2</sub>, COOH, CO<sub>2</sub>CH<sub>3</sub> etc

Fig. 2 Arylation of CNTs *via* reduction of diazonium salts, where R = Cl, NO<sub>2</sub>, COOH, CO<sub>2</sub>CH<sub>3</sub> etc.



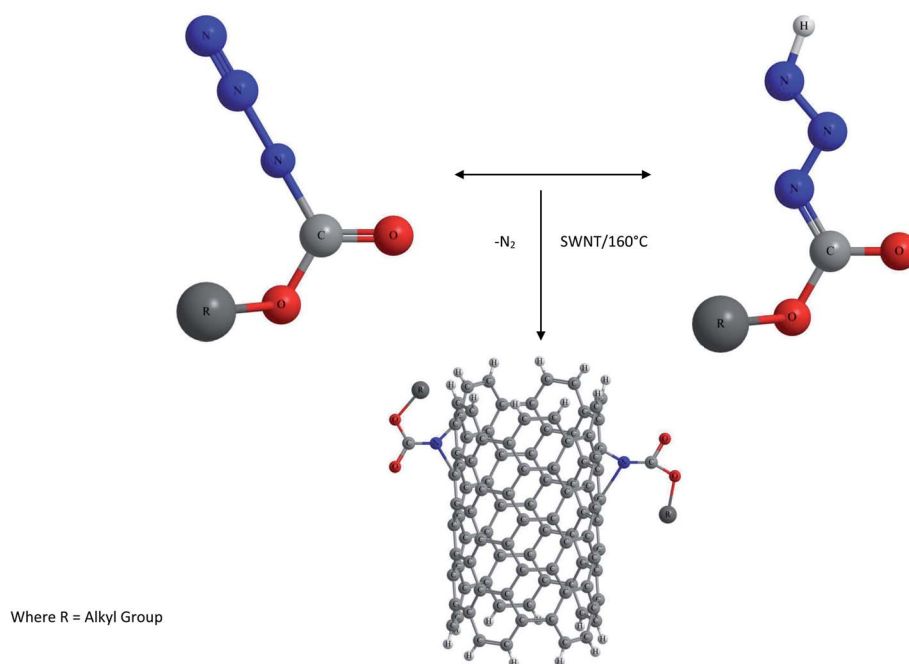


Fig. 3 Functionalization of CNTs with nitrenes, where R = alkyl group.

the chlorine atoms with hydroxyl groups, which in a second step were esterified to yield corresponding esters as shown in Fig. 5.

This functionalization of SWCNTs not only resulted in a soluble functionalized material but also showed that specifically derivatized CNTs bearing free functional groups on their skeleton can serve as suitable synthons for the multistep synthesis of CNT based materials.

(vii) *Functionalization of CNTs with a metal-containing molecular complex.* Both raw and oxidized CNTs have been functionalized with Vaska's compound  $trans\text{-IrCl}(\text{CO})(\text{PPh}_3)_2$  to form a covalent CNT-metal complex by coordination through the increased number of oxygen atoms, and formed a hexacoordinate structure around the Ir atom<sup>70</sup> respectively. The complexes of oxidized nanotubes with Vaska's compound were soluble and stable in organic solutions compared to raw and

oxidized tubes. Moreover the tubes could be easily recovered from solution. The novelty of this derivatization is that the nanotube can be considered as a primary ligand, as a functional moiety like any other, with respect to the central metal atom, Ir. In effect, Ir was found to coordinate with the nanotubes in several distinctive bonding arrangements, depending on the oxidation state of the nanotubes. Thus the electronic structure of nanotubes is preserved due to functionalization through coordinate attachment. A similar type of functionalization has also been observed with Wilkinson's complex,  $\text{RhCl}(\text{PPh}_3)_3$ .<sup>71</sup> Hence, this functionalization opens up the area of metallo-organic chemistry suggesting potential application in catalysis and molecular electronics.

2.1.1.2 *Covalent functionalization by derivatization of functional groups*

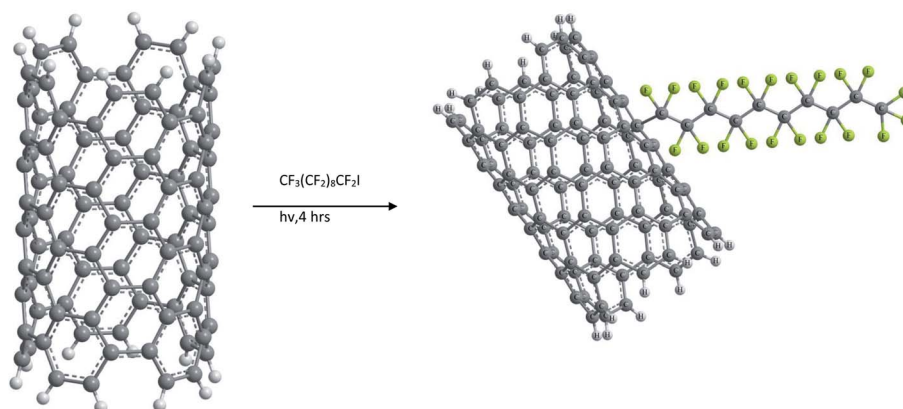


Fig. 4 Functionalization of CNTs with radicals.



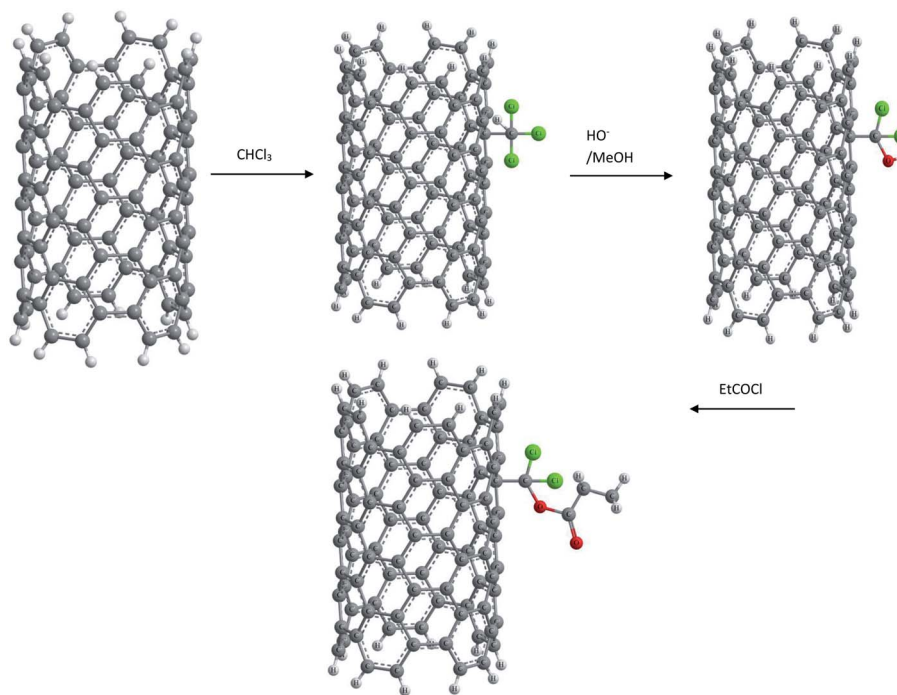



Fig. 5 Electrophilic addition reaction of CNTs, where R = alkyl/aryl group.

(1) *Carboxylation and further derivatization.* The purification of CNTs involves the removal of metal particles or amorphous carbon from the crude material by oxidative methods in strong acidic media.<sup>72,73</sup> Under such harsh conditions, the end caps of the nanotubes get opened and become acidic ( $-\text{COOH}$ ) and other ( $-\text{OH}$ ) functionalities suitable for further derivatization are formed at the tips as well as on the side walls.<sup>74-76</sup> The tip functionalized CNTs can form a closed ring shape, or even function as single molecular sensors or probes, whereas surface functionalized CNTs can be used as a molecular linker to interconnect nanotubes<sup>77</sup> as shown in Fig. 6.

For carrying out the functionalization of CNTs by oxidation, potassium permanganate has been used as the oxidant in the

presence of sulfuric acid. It has also been used along with a phase transfer catalyst.<sup>78</sup> Other oxidants used to functionalize CNTs are concentrated nitric acid, concentrated sulfuric acid, a mixture of concentrated sulfuric and nitric acid, superacid  $\text{HF}/\text{BF}_3$ , aqua regia, aqueous  $\text{MO}_4$  ( $\text{M} = \text{Os}, \text{Ru}$ ),  $\text{OsO}_4\text{-NaIO}_4$ ,  $\text{H}_2\text{O}_2$ ,  $\text{K}_2\text{Cr}_2\text{O}_7$  etc.<sup>79,80</sup> However some of these reagents open the tips of the tubes, causing damage to the tubular structure, or even introducing contaminants.

(1) *Amidation and esterification of  $-\text{COOH}$  groups via covalent linkages.* Generally activation of carboxyl moieties with thionyl chloride and subsequent reaction with amines are preferred as shown in Fig. 7, or alternatively, direct condensation of oxidized NTs with amines is also carried out.<sup>81</sup>

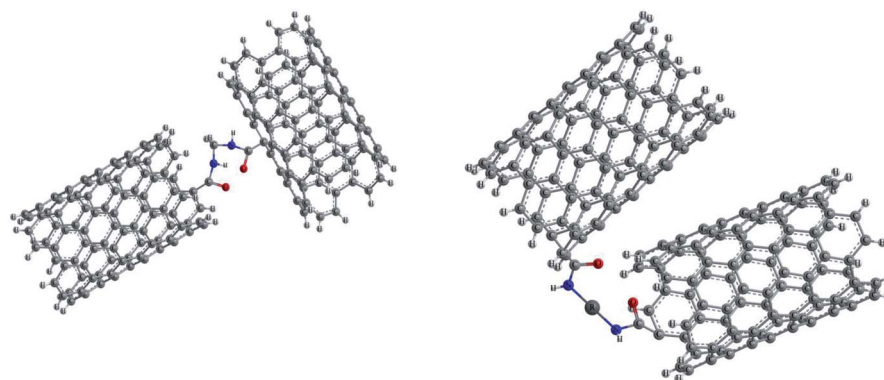

Where R = Alkyl/Aryl Group

Fig. 6 Linking of CNTs via surface and tip functionalized groups.



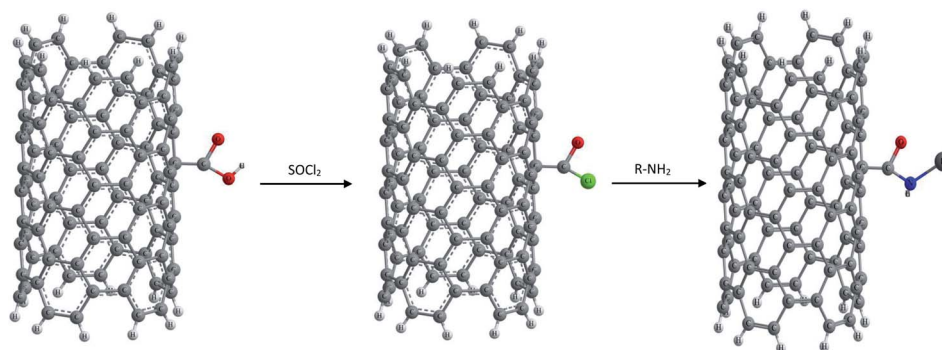


Fig. 7 Amidation of COOH functionalized CNTs.

Niyogi and co-workers first reported the use of acid groups for attaching long alkyl chains to SWCNTs *via* amide linkages. Thus long chain alkylamines were condensed with carboxylic groups present on the surface of CNTs.<sup>82</sup> The amido functional NTs were found to be soluble in solvents such as tetrahydrofuran or dichlorobenzene. Sun and coworkers showed that the esterification of carboxylic acids results in functionalization as well as solubilization of nanotubes of any length.<sup>83,84</sup> Thus the amidation and esterification reactions of oxidized NTs have been reported which finally result in soluble functionalized CNTs.<sup>85,86</sup> An advantage with ester linkages is that they can be facilely defunctionalized *via* acid or base catalyzed hydrolysis, allowing the recovery of carbon nanotubes from the soluble samples.

**(2) Ionic functionalization of -COOH groups.** Non-covalent functionalization of -COOH groups present on the surface of pure SWCNTs has been carried out by reacting with octadecylamine.<sup>87</sup> The acid base reaction leads to the formation of SWCNT-carboxylate zwitterions as shown in Fig. 8. These zwitterions are soluble in THF and 1,2-dichlorobenzene and partially in dichloromethane, chlorobenzene *etc.* This ionic functionalization approach shows advantages such as a high yield ( $\sim 70\%$ ) of soluble NTs compared to that obtained in covalent functionalization ( $\sim 30\%$ ).

Further the presence of zwitterions improves the solubility of purified CNTs significantly and the acid base reaction

represents the simplest possible route to soluble SWCNTs and can be readily scaled up at low cost. Unlike the covalent amide bond, the cation ( $^+\text{NH}_3(\text{CH}_2)_{17}\text{CH}_3$ ) in the ionic bond of the  $(\text{SWCNT-COO}^-)^+\text{NH}_3(\text{CH}_2)_{17}\text{CH}_3$  of soluble SWCNTs can be readily exchanged for other organic and inorganic cations. Thus it is possible to adjust the solubility properties of SWCNTs and to use soluble SWCNT (*s*-SWCNTs) as versatile building blocks for advanced SWCNT-based materials *via* supramolecular chemistry. Furthermore, such an ionic feature allows electrostatic interactions between SWCNTs and biological molecules and can serve as the basis for developing biocompatible SWCNTs.

**(II) Attachment of metallic nanoparticles.** Carboxylic and hydroxyl functionalized carbon nanotubes have also been used for nanoparticle deposition by reducing metal precursors in ethylene glycol solutions.<sup>88–90</sup> Several researchers have reported deposition of Pt, Ru and alloy PtRu nanoparticles by this method.<sup>91,92</sup> Nanoparticles of 1–10 nm with metal loading less than 10 wt% have been obtained. Deposition of Pt nanoparticles has also been reported on sulfonic acid functionalized CNTs in which the sulfonic acid sites act as molecular sites for Pt ion adsorption, which get subsequently reduced to yield small Pt nanoparticles.<sup>93</sup> Au has been deposited on CNTs by using a large variety of functional groups. For example Au nanoparticles were successfully self-assembled on the surface of MWCNT functionalized with mercaptobenzene moieties.<sup>94</sup> On the other

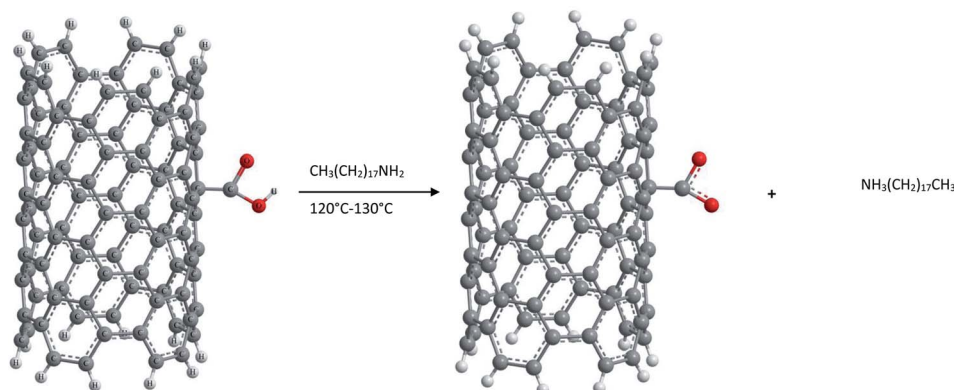


Fig. 8 Ionic functionalization of COOH functionalized CNTs.



hand, Muhammad *et al.* reported deposition of Au nanoparticles on ethylenediamine functionalized SWCNTs.<sup>95</sup> It was found that the Au NPs acted as an electron acceptor to the amine functionalized SWCNTs. Jiang *et al.* also attached Au NPs to nitrogen doped MWCNTs with a  $\text{H}_2\text{SO}_4\text{-HNO}_3$  chemical treatment.<sup>96</sup> Ellis *et al.* demonstrated novel anchoring of gold nanoclusters onto CNTs *via* hydrophobic interactions between octanethiol capped nanoclusters and acetone activated CNT surfaces.<sup>97</sup> According to Hwang *et al.* copper has also been uniformly deposited on functionalized MWCNTs by chemical methods.<sup>98</sup> Recently, a novel type of Pd coated MWCNT has been reported by Adeli *et al.*<sup>99</sup> They polymerized citric acid on the surface of functionalized ( $-\text{COOH}$ ) MWCNTs resulting in MWCNT-*graft*-poly(citric acid) (MWCNT-*g*-PCA) hybrid materials. These materials were not only soluble in water but were also able to trap water soluble metal ions. Reduction of trapped metal ions in the polymeric shell of MWCNT-*g*-PCA hybrid materials by reducing agents such as sodium borohydride led encapsulated metal nanoparticles on the surface of the MWCNTs.

**2.1.2 Noncovalent functionalization.** Non covalent treatment is particularly attractive because of the possibility of adsorption of various groups on the CNT surface without disturbing the  $\pi$  system of the graphene sheets.<sup>100</sup> Non-covalent approaches are based on interactions of the hydrophobic part of

the adsorbed molecules with nanotube sidewalls through van der Waals,  $\pi$ - $\pi$ , CH- $\pi$  and other interactions, and aqueous solubility is provided by the hydrophilic part of the molecules.<sup>101</sup> The charging of the nanotube surface due to adsorbed ionic molecules additionally prevents nanotube aggregation by the coulombic repulsion forces between modified CNTs. In the last few years, the noncovalent treatment of CNTs with surfactants and polymers has been widely used in the preparation of both aqueous and organic solutions to obtain a high weight fraction of individually dispersed nanotubes.

**2.1.2.1 Surfactant functionalization.** Surfactants generally act as “solubilizers” and disperse CNTs *via* physical adsorption. Generally the hydrophobic part of surfactants is oriented towards the surface of CNTs, whereas the polar moiety interacts with solvent molecules in the outer region as shown in Fig. 9. Both ionic and non-ionic surfactants such as sodium dodecyl sulphate (SDS), sodium dodecyl benzene sulfonate (SDBS), cetyltrimethyl ammonium bromide (CTAB), Brij, Tween, Triton X, and a siloxane polyether copolymer (PSPEO) have been used for dispersion of CNTs in an aqueous medium.<sup>102-106</sup> It is believed that the nanotubes are in the hydrophobic interiors of the corresponding micelles, which results in stable dispersion. However, the nature and concentration of the surfactant plays a very important role in obtaining stable dispersions.

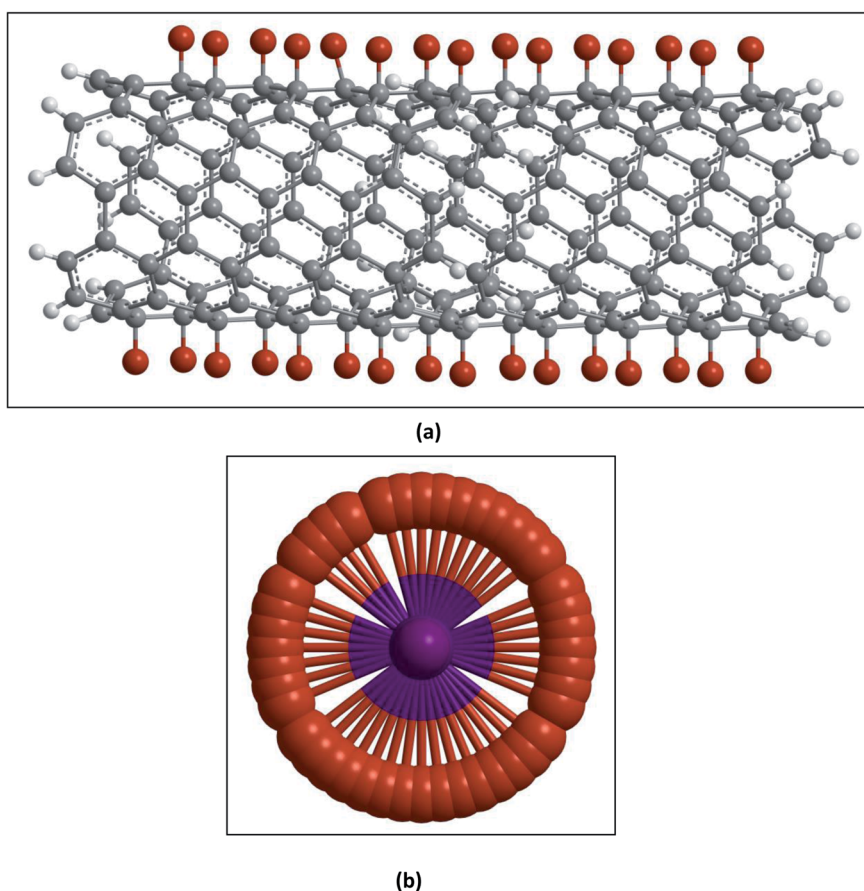


Fig. 9 Surfactant functionalization of CNTs (a) and a surfactant micelle (b).



Dispersion/solubilization is generally achieved by placing CNTs in a solution of surfactant and sonication in an ultrasonic bath. During sonication, the provided mechanical energy overcomes the van der Waals interactions in the CNT bundles and leads to CNT exfoliation, and at the same time the surfactant molecules are adsorbed onto the surface of the CNT walls.<sup>107</sup> The colloidal stability of the dispersion of the CNTs with adsorbed molecules on their surface is guaranteed by electrostatic and/or steric repulsion.<sup>108–111</sup> Y. Shi *et al.*<sup>112</sup> reported the preparation of individually dispersed SWCNTs by sonication in a micelle of SDS. Gao *et al.*<sup>113</sup> obtained a homogeneous dispersion of MWCNTs at the optimum composition of 0.5 wt% MWCNTs and 2 wt% SDS relative to water. The interaction between CNTs and SDS through the hydrophobic segment causes a steric repulsion and higher negative surface charge, which improves the dispersion of CNTs. Thus the charge of ionic surfactants leads to electrostatic repulsion between the surfactant molecules, and this stabilizes the nanotube colloids, whereas the non-ionic surfactants stabilize the nanotubes in solution primarily by steric interactions. Compared to traditional alkyl chain surfactants, silicone polymer surfactants possess better properties such as super wettability and extremely low surface tension.<sup>114</sup> PSPEO, a new amphiphilic macromolecule surfactant, consists of hydrophobic –Si–O–Si– main chains and hydrophilic pendant parts of polyethylene oxide, with a comb-polymer molecular structure. MWCNTs can be easily solubilized in water by non-covalent functionalization with PSPEO.<sup>102</sup>

**2.1.2.2 Polymer wrapping.** Amphiphilic polymers are also used to solubilize CNTs. The main advantage of using polymers instead of small molecular surfactants is that polymers reduce the entropic penalty of micelle formation. It has been reported that some conjugated polymers have significantly higher energy of interaction with nanotubes than small molecules. O'Connell *et al.*<sup>115</sup> reported that SWCNTs can be reversibly solubilized in water in the  $g\ L^{-1}$  concentration range by noncovalent association with a variety of linear polymers such as polyvinyl pyrrolidone (PVP) and polystyrene sulfonate (PSS).

PVP, a polymer with a hydrophobic alkyl backbone and hydrophilic pendant groups, gets coiled around the nanotube in a manner depicted in Fig. 10 such that its backbone is in contact with the nanotube surface and pyrrolidone groups are exposed to water.<sup>116</sup> But the CNTs were found to unwrap on changing the solvent system. S. H. Tan *et al.*<sup>117</sup> reported successful functionalization of MWCNTs with water soluble poly(2-ethyl-2-oxazoline) (PEOX) through the polymer wrapping process. The functionalized MWCNTs gave excellent and stable dispersion in

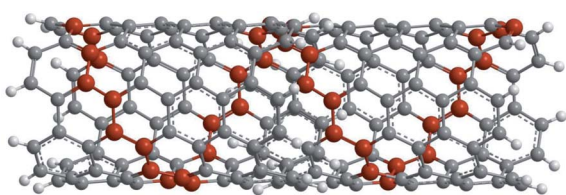


Fig. 10 Functionalization of CNTs *via* polymer wrapping.

water as well as other organic solvents such as ethanol and *N,N*-dimethylformamide (DMF). Compared to PVP, polynucleotides are arranged in an opposite manner on CNTs due to their hydrophilic sugar phosphate backbone and relatively hydrophobic aromatic nucleotide bases present as pendants. They form various helical wrappings around the nanotube so that aromatic nucleotide bases are in close contact with the SWCNTs.<sup>118</sup> Wrapping of polymers based on conjugated poly(*m*-phenylenevinylene) (PmPV) systems is also very important as it allows the formation of very effective van der Waals interactions between the nanotubes and the conjugated backbone.<sup>119,120</sup> Tang B. Z. *et al.*<sup>121</sup> synthesized poly(phenyl acetylene) wrapped carbon nanotubes (PPAc-CNTs) which were soluble in organic solvents such as tetrahydrofuran, toluene, chloroform and 1,4-dioxane by *in situ* polymerization. Biological molecules such as peptides and proteins have also been reported to interact with the sidewalls of SWCNTs and make them more soluble in solvents.

**2.1.2.3 Polymer absorption.** Pyrenes, a group with a large aromatic system, have demonstrated very high affinity for the nanotube surface and are hence considered an efficient moiety for noncovalent functionalization,<sup>122</sup> as shown in Fig. 11. In fact the interaction of the pyrene aromatic system with nanotubes is so effective that functionalized pyrenes have been used for anchoring proteins and small biomolecules. For example R. J. Chen *et al.* developed a method for the immobilization of proteins and small biomolecules into succinimidyl pyrenebutyrate modified SWCNTs.<sup>123</sup> In addition, pyrenes bearing hydrophilic groups such as ammonium ions, carboxylates and block copolymer components give rise to tubes with aqueous solubility. Anthracenes are another class of polyaromatic molecules forming specific  $\pi$ - $\pi$  interactions with nanotubes. However, anthracenes can be replaced by pyrenes which show stronger interactions with nanotubes. Heterocyclic polyaromatic molecules such as porphyrins and phthalocyanines can also form effective interactions with nanotubes. Nakashima *et al.* found that porphyrin has the ability to disperse SWCNTs for long periods in organic solvents.<sup>124</sup>

**2.1.2.4 Polymer encapsulation.** Encapsulating CNTs with polymers is used as an advantageous alternative approach to realize surface modification. Being a non covalent process, it offers the advantage of maintaining the inherent electronic properties of CNTs. For example, polymer encapsulated MWCNTs have been successfully prepared by Wang *et al.* through ultrasonically initiated *in situ* emulsion polymerizations of *n*-butyl acrylate (BA) and methyl methacrylate (MMA) in the presence of MWCNTs.<sup>125</sup> The polymer encapsulated CNTs showed strong interactions between the polymer and MWCNT and they could be well dispersed in polymer matrices such as Nylon 6. In addition to encapsulation of MWCNTs, SWCNTs were also encased within crosslinked/hyperbranched amphiphilic copolymer micelles.<sup>126,127</sup> The results showed that the dispersion performance of the obtained micelle encapsulated CNTs in water was greatly improved compared to that of pure CNTs. Stupp *et al.* reported encapsulation of both single and multiwall carbon nanotubes by self assembling peptide amphiphiles.<sup>128</sup> CNTs have also been encapsulated inside



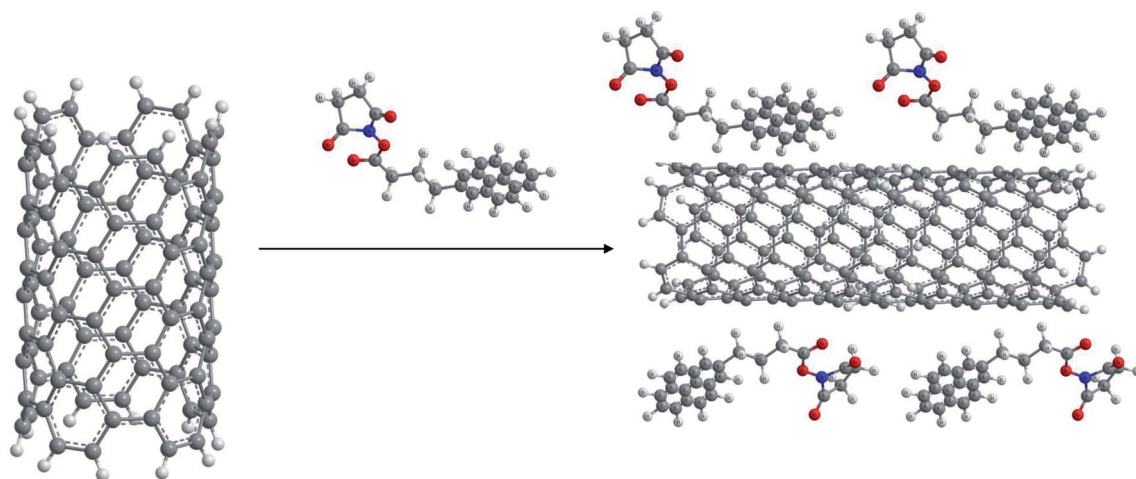


Fig. 11 Functionalization of CNTs by substituted pyrenes.

polyamide microcapsules for the development of remotely triggerable microcapsules.<sup>129</sup> Such encapsulations enhance the dispersion of CNTs significantly in a wide variety of polar and non-polar solvents and polymer matrices.

**2.1.2.5 Metal deposition.** In addition to deposition of various metals on functionalized CNTs, different types of metals have successfully been deposited on unfunctionalized CNTs also. Different strategies involved are electrochemical deposition, electroless deposition with and without the aid of reducing agents and physical/chemical deposition on CNTs without surface activation. Among these, electroless deposition is of particular interest because of its simplicity and feasibility for large scale production of nanotube–nanoparticle hybrids. The electroless deposition of a large variety of metal nanoparticles including Cu and Ag has been reported on both SWCNTs and MWCNTs in the absence of any reducing agents.<sup>130</sup> Dai and coworkers reported the spontaneous nucleation of bare Pt and Au particles on SWCNT side walls.<sup>131</sup> Sometimes NTs were found to be oxidatively consumed in the process. Lemay *et al.* demonstrated electrodeposition of Au, Pt and Pd nanoparticles on the sidewalls of SWCNTs under direct potential control where the nanotube acts as a nonsacrificial template for the deposited clusters.<sup>132</sup> Here the nanotube shows a dual function: initially as an electrodeposition template and subsequently as a wire to electrically connect the deposited Au, Pt and Pd nanoparticles. Spontaneous deposition of Pt and Au NPs on the sidewalls of single and multiwall CNTs was also reported by Wu

*et al.*<sup>133</sup> The studies showed that metal ions were first adsorbed on the sidewalls of CNTs and then were reduced by ethanol. Zhang *et al.* reported continuous and quasi-continuous coating of various metals such as Ti, Ni and Pd on suspended SWCNTs by electron beam evaporation<sup>134</sup> resulting in metal nanotube supported metal nanowire structures.

## 2.2 Endohedral functionalization

Endohedral functionalization is of particular interest since the interior of carbon nanotubes is considered as a nanometer sized test tube which provides a highly unexplored, ultrapure nanospace where new reactions may be observed which do not take place outside the tubes.<sup>135</sup> The interior surface of CNTs also exhibits a stronger binding energy for adsorbate molecules compared to the planar carbon surface, as expected for a molecule in close proximity to the curved internal surface of the tube.<sup>136,137</sup> In addition, the inner cavity of CNTs offers space for the storage as well as protection of guest molecules.

**2.2.1 Metal encapsulation.** At present, CNT encapsulated metallic materials have aroused great interest around the world due to the fact that the protective carbon layers prevent rapid oxidation of bare metal nanoparticles. Generally, encapsulation can be carried out by two methods either during CNT synthesis itself that is an *in situ* process or by wet chemical methods of opening and filling the nanotubes. Both processes have been widely studied. Various techniques have been developed for synthesizing *in situ* metal filled CNTs, such as the standard carbon arc technique, modified arc deposition or catalytic pyrolysis. Nanoparticles of nearly 15 metals (including Fe, Co, Ni, Ti, Cu and a few rare earth metals and metal carbides) have been successfully encapsulated in CNTs by including the metals in the carbon arc commonly used to synthesize the nanotubes.<sup>138–140</sup> Several groups have studied the filling of CNTs by wet chemical methods.<sup>74,141</sup> Small quantities of low melting metals such as lead, zinc, selenium and molten silver nitrate have also been incorporated into nanotubes through capillary action after the closed ends of nanotubes were partially opened chemically.<sup>142</sup> To date, the uptake and the endohedral chemistry

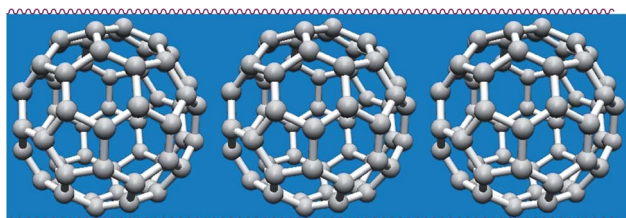


Fig. 12 Fullerene encapsulation inside CNTs.



of metals and metal salts have been intensively investigated. For example, gold and platinum nanothreads have been created in the capillaries of the tubes, by treating the SWCNTs with the

corresponding perchlorometallic acids at high temperatures. In some cases, the resulting nanothreads have been found to be single crystals.

Table 5 Application of functionalized CNTs

f-CNT compound (chemical structure)	Application area	Advantages offered	References
Polyethylene/polystyrene/PMMA-covalently functionalized SWCNTs	Advanced polymeric nanocomposites	Enhanced dispersion of CNTs in polymer matrices Increased interfacial bonding	43 and 161–165
Polymer encapsulated CNTs–Nylon 6 nanocomposite	Advanced polymeric nanocomposites	Improved interfacial adhesion between polymer encapsulated CNTs and Nylon 6	125
Metal NP supported CNTs	Catalysis	Improved catalytic activity and selectivity	168–173
CNTs functionalized with Vaska's compound	Catalysis and molecular electronics	Enhanced solubility with solution durability	70
CdSe QDs loaded multiamino f-CNTs & magnetic Fe <sub>3</sub> O <sub>4</sub> NPs for nano sensors, optoelectronics	Nano sensors, optoelectronics, catalysis <i>etc.</i>	Optical property of QDs and magnetic properties of Fe <sub>3</sub> O <sub>4</sub> nanoparticles were maintained	174
Metal coated and metal filled CNTs SWCNTs/PmPV	Stealth technology Photovoltaic devices	Enhanced EM absorbing properties Enhanced optoelectronic properties	175 and 176 119 and 120
Immobilization of DNA, proteins, oligonucleotides <i>etc.</i>	Miniaturized novel biosensors	Coupling of NTs electronic properties with recognition properties of immobilized biosystems	177–181
Chemically functionalized CNTs	Substrate for neuronal growth	Controlled neuronal processes by charge manipulation of f-CNTs	182
Glucose oxidase attached CNTs	Single-molecule biosensors	Controlled enzymatic activity	183
Covalently linked nanotube peptide conjugates	New bioactive nanomaterials	Enhanced <i>in vivo</i> antibody response	185 and 186
Peptide wrapped SWCNTs	Designing & identification of peptide sequences	Identification using phage display	187
f-SWCNTs-ethylene oxide surfactants, 4-hydroxynonenal-MWCNTs	Biomolecular recognition	Detection of antibodies binding Adsorption of specific antibody	188
CNTs and telomeric DNA fragment containing noncanonical G-quadruplex and i-motif forms	Molecular dynamics simulation studies	Encoding of CNTs with tubular nucleic acids for information storage	189–191
Functionalized and cross linked CNTs	Water purification	Highly efficient and targeted removal of chemical and biological contaminants	192, 193, 205, 207, 208, 210 and 211
Metal oxide coated CNTs	Electrocatalytic water treatment	Treatment by electrocatalytic process	194 and 195
Magnetic CNTs, f-CNTs	Separation of hydrocarbon and oil from water	Enhanced separation capacity	196–199
Rim functionalized CNTs, zwitterion functionalized CNTs/polyamide nanocomposite membranes, electrochemically modified CNTs	Water desalination	Enhanced performance	200–203
Amine functionalized multi walled carbon nanotubes (MWCNTs)-polyimide membranes	Organic solvent nanofiltration	Enhanced flux	204
PEG-CNTs	Battery wastewater	Specific removal of chromium and zinc	206
Functionalized CNTs	Drug delivery	Biocompatibility and targeted drug delivery	212, 213, 215–217 and 221
Polymeric nanohybrids and f-CNTs	Drug delivery	Targeted drug delivery for cancer therapy	214
COOH functionalized SWCNTs	Drug delivery	Targeted delivery of cladribine and flutamide anticancer drug for in a gas phase and water solution	218 and 219
PEG-SWCNTs	Drug delivery	Targeted drug delivery for cancer	220



**2.2.2 Fullerene encapsulation.** The incorporation of fullerenes such as C<sub>60</sub> and C<sub>70</sub> (ref. 143–150) or metallofullerenes such as Sm@C<sub>82</sub> (ref. 151–153) is an especially impressive example of the endohedral chemistry of SWCNTs (Fig. 12). This incorporation is executed at defect sites localized at the ends or in the sidewalls. The encapsulated fullerenes tend to form chains that are coupled by van der Waals forces. Such arrays are sometimes called <sup>TM</sup>bucky peapods, which are considered a very interesting and curious material among novel types of nanotube composites.

Peapods were first revealed by Luzzi *et al.*<sup>154</sup> and then were synthesized in high yield by Burtiaux *et al.*<sup>155</sup> Upon annealing, the encapsulated fullerenes coalesce in the interior of the SWCNTs, which results in new, concentric, endohedral tubes, with a diameter of 0.7 nm.

**2.2.3 Miscellaneous.** In addition to metal and fullerenes, other types of materials such as halogen elements have also been encapsulated inside CNTs.<sup>156,157</sup>

### 3. Important properties of functionalized CNTs

A variety of oligomeric and polymeric compounds have been used in the functionalization of CNTs due to their solubility in common organic solvents and water.<sup>158–160</sup> This functionalization breaks nanotube bundles, which is essential to the solubility. For example the carboxylic groups of f-CNTs could be ionically bound to metal ions, or get covalently linked through different organic groups. Increased solubility due to exfoliation of the nanotube bundles is the most important, common, and frequently reported property of functionalized CNTs. The amide and ester functionalities dramatically improve their solubility in organic solvents. Similar solubility properties were also obtained for amine zwitterion functionalized SWCNTs. In addition, polymer wrapped CNTs are also among the most soluble samples. SWCNTs and MWCNTs functionalized with highly soluble PPEI-EI, PVA-VA and PEO polymers as well as with PEO-derived dendron moieties are soluble not only in organic solvents but also in water. Glucosamine and protein conjugates with CNTs are highly soluble in water. Attaching transition metal complexes to nanotubes increases their solubility in dimethylformamide, dimethylsulphoxide, tetrahydrofuran, methanol, chloroform, toluene *etc.* Strong luminescence was reported for CNTs chemically bound to PPEI-EI, PVA-VA polymers, and PEO derived dendron moieties. Luminescence quantum yields were found to be substantial, 11% for MWCNT-PPEI-EI in chloroform at 400 nm excitation.

### 4. Applications of functionalized CNTs

Functionalized CNTs find wide application in different areas of materials science, biomedical science, water purification and drug delivery systems as depicted in Table 5. The details are discussed below:

#### 4.1 Materials science

In the area of materials science, f-CNTs are being widely used for the development of high quality nanocomposites. The use of f-CNTs for fabricating advanced polymeric composites<sup>43,161–163</sup> offers significant advantages over the use of non functionalized CNTs, by increasing the dispersion of carbon nanotubes in polymeric matrices. The functional moiety increases the interfacial bonding, thereby, lessening fiber pullout during mechanical stress or entanglement in contrast to unfunctionalized CNTs where dispersion and interfacial bonding or entanglement is minimal. For example covalently functionalized SWCNTs have been used as fillers at >1 wt% concentration in polymeric hosts such as PMMA, PS, *etc.* For PMMA, tensile modulus increased by more than a factor of 2 with only 0.1 wt% f-SWCNTs added and for polystyrene f-SWCNT nanocomposites a substantial increase in viscosity and elasticity of the system was observed at low shear rates even at 1 wt% loading compared to 3 wt% pristine CNT loading which remained like a liquid.<sup>164,165</sup> It was found that polymer encapsulated CNTs could be well dispersed in a Nylon 6 matrix compared to unmodified CNTs, due to improved interface adhesion between the polymer encapsulated CNTs and Nylon 6. It was found that yield strength improved by 30% and Youngs modulus by 35% at only 1 wt% content of polymer encapsulated CNTs.<sup>125</sup> Thus the solubilization of CNTs *via* chemical functionalization is an effective approach to achieve a homogeneous dispersion of CNTs in polymer matrices for high quality nanocomposites.

Functionalized CNTs also possess wide application in catalysis by acting as support materials. V. O. Nyamori *et al.* reviewed various surface functionalization techniques for improving CNT properties for use as a catalyst support, and also available methods for catalyst nanoparticles loading on f-CNTs.<sup>166</sup> B. Ye *et al.*<sup>167</sup> reported oxygen functionalized CNTs for selective catalytic reduction of NO<sub>x</sub> with NH<sub>3</sub>. Oxygen functional groups were generated on the surface of CNTs by acid treatment, which acted as anchoring sites for nanoparticles of different metals. The synthesized functional materials exhibited an enhanced NO<sub>x</sub> removal efficiency of over 90% at 350–380 °C. More studies have been carried out in order to demonstrate that metal nanoparticles supported on carbon nanotubes provide much improved catalytic activity.<sup>168–172</sup> Q. Wang *et al.* have<sup>173</sup> reported that Pt nanoparticles deposited on Nafion® functionalized CNTs show much higher catalytic activity for the oxygen reduction reaction. The synthesized material also showed a slower decomposition rate in an electrochemically accelerated durability test making it a potential electrocatalyst for fuel cell applications.

In addition to metal coated CNTs, metal filled CNTs also have shown promising applications in heterogeneous catalysis. Gao *et al.* reported a simple strategy for loading multiamino f-CNTs with CdSe QDs and magnetic Fe<sub>3</sub>O<sub>4</sub> nanoparticles *via* electrostatic attractions. It was observed that both the optical properties of QDs and magnetic properties of Fe<sub>3</sub>O<sub>4</sub> nanoparticles were maintained and the resulting products showed potential applications in nano sensors, optoelectronics, catalysis and other fields.<sup>174</sup> In addition to catalysis, metal coated



and metal filled CNTs find wide application in stealth technology due to their EM absorbing properties.<sup>175,176</sup>

## 4.2 Biomedical science

Immobilization of biomolecules on CNTs for coupling the electronic properties of NTs with the specific recognition properties of the immobilized biosystems has motivated researchers to use CNTs as a new type of miniaturized biosensor materials.<sup>177,178</sup> For example metallothionein proteins were trapped inside and placed on to the outer surfaces of open ended MWCNTs.<sup>179,180</sup> Streptavidin was also found to adsorb on MWCNTs presumably *via* hydrophobic interactions between the nanotubes and hydrophobic domains of the proteins. DNA molecules adsorbed on MWCNTs *via* non specific interactions were also observed.<sup>178–180</sup> In addition to MWCNTs, SWCNTs have also been noncovalently functionalized, and various biological molecules have subsequently been immobilized onto f-SWCNTs with a high degree of control and specificity.<sup>181</sup> Haddon *et al.*<sup>182</sup> reported the use of chemically modified CNTs as a substrate for growth of neurons. It was observed that by manipulating the charge carried by f-CNTs the outgrowth and branching pattern of neuronal processes could be controlled. Dekker *et al.*<sup>183</sup> reported that redox enzyme glucose oxidase when attached to CNTs preserved their enzymatic activity. Also, the enzyme-coated tube was found to act as a pH sensor with large and reversible changes in conductance upon changes in pH.


Different types of biomolecular interactions with CNTs sidewalls have been explored extensively. For example water soluble IPEG-SWCNT samples have been used as a starting material in the exchange reaction with bovine serum albumin (BSA) protein under ambient conditions for the preparation of SWCNTs–BSA conjugates. I<sub>PEG</sub>-SWCNTs is also soluble in organic solvents such as chloroform, but the SWCNTs–BSA conjugate is only soluble in water. Thus the solubility change acts as an indicator for ester to amide transformation in the transformation reaction. The TEM results have confirmed that the conjugate sample contains well dispersed SWCNTs.

Functionalized carbon nanotubes have also been reported for targeting of Amphotericin B to cells.<sup>184</sup> The association of CNTs with peptides is expected to be useful in biosensor applications and in the development of new bioactive nanomaterials. For example Pantarotto *et al.*<sup>185</sup> demonstrated an enhanced *in vivo* antibody response from covalently linked nanotube peptide conjugates and Wang *et al.*<sup>186</sup> reported identification of peptide sequences having specific affinities for CNTs by using a phage display. Zorbas *et al.*<sup>187</sup> designed an amphiphilic peptide sequence which folds into an  $\alpha$ -helix on nanotube sidewalls. For sensing Shim *et al.*<sup>188</sup> functionalized substrate grown SWCNTs with ethylene oxide based surfactants. Subsequently these non-ionic surfactants were associated covalently with proteins to electrically detect the binding of antibodies. MWCNTs have been functionalized with 4-hydroxynonenal (4-HNE) to induce adsorption of 4-HNE antibody. This effect is interesting for the development of biosensors, because the electronic properties of the tubes can be combined with the recognition properties of the immobilized biosystems. In

addition to this, molecular dynamics simulation studies have been carried out for systems composed of CNTs and Telomeric DNA fragment containing noncanonical G-quadruplex and i-Motif forms.<sup>189,190</sup> Y. Zhang *et al.* also reported the encoding of CNTs with tubular nucleic acids for information storage, as DNA interacts with CNTs in a sequence specific manner resulting in different conformations including helix, i-motif, and G-quadruplex.<sup>191</sup>

## 4.3 Water purification

Research on safe effective and economic materials that can eliminate current and future contaminations from water is a scientific and technological issue of primary importance to the scientific community and scientists all over the world are deeply involved in this research. Among many materials developed for the said purpose CNTs especially functionalized carbon nanotubes have been widely researched for the said application. K. M. Lee *et al.*<sup>192</sup> reviewed the adsorptive potential of f-CNTs for removal of water pollutants. M. Barrejón *et al.* studied the adsorptive removal of water contaminants by using chemically crosslinked SWCNTs.<sup>193</sup> They reported that the cross-linked CNT adsorbents exhibited selective sorption capability along with good recyclability for removal of oils and organics from contaminated water. Jame *et al.*<sup>194</sup> reviewed the use of electrochemically active CNTs filters as an efficient technology for water and wastewater treatment targeting chemical and biological contaminants. The advantage of using electrochemically active CNTs filters is that they provide additional electrooxidation of the adsorbed contaminants thus increasing the effectiveness of treatment. The working principles, impacting factors and latest developments of electrochemically active CNT filters along with challenges and future perspectives have been discussed. S. Y. Yang *et al.*<sup>195</sup> studied metal oxide modified CNTs filters for electrocatalytic water treatment especially for the removal of phenol. It was observed that the performance of modified CNT performance was approximately twice when compared to that with bare CNT filters. In the wide spectrum of water contaminants magnetic CNTs (MCNTs) have been used by Wang *et al.*<sup>196</sup> for the removal of oil droplets from contaminated water. The authors have designed, fabricated and experimentally evaluated superparamagnetic iron oxide nanoparticle (SPIONs) decorated CNTs for oil–water separation. They have shown that the synthesized material removes oil through a two step mechanism, where in the first step MCNTs get dispersed at the oil–water interface and in the second step drag the oil droplets with them out of water by a magnet. They have also mentioned that 80% of the separation capacity could be restored by a 10 min wash by using 1 ml ethanol for every 6 mg of MCNTs. J. Liu *et al.*<sup>197</sup> used functionalized multiwalled carbon nanotubes for separation of emulsified oil from oily wastewater. According to a recent article by N. Al-Jammal<sup>198</sup> functionalized carbon nanotubes have been used for hydrocarbon removal from water. As per a recent report by T. A. Abdullah *et al.*<sup>199</sup> f-CNTs have been successfully used for oil spill clean up from water. Functionalized CNTs have also been used for desalination. Y. Hong *et al.* reported the use of rim



functionalized carbon nanotubes for water desalination.<sup>200</sup> In a membrane form, zwitterion functionalized carbon nanotube/polyamide nanocomposite membranes have been used for water desalination.<sup>201</sup> Z. Z. Chowdhury *et al.*<sup>202</sup> reviewed the physio-chemical aspect along with the working mechanism of electrochemically modified CNT membranes for desalination and water purification. Das *et al.*<sup>203</sup> reported the synthesis and evaluation of functionalized carbon nanotube based polymer composite nanofiltration membranes for desalination. Farahani<sup>204</sup> *et al.* also reported the study of amine functionalized multi walled carbon nanotube (MWCNTs) based nanofiltration membranes for desalination due to their high adsorption capacity. I. G. Werten *et al.*<sup>205</sup> reviewed the progress of CNT functionalization applied to membrane filtration with respect to membrane properties and their performance. W. A. Hamzat *et al.*<sup>206</sup> studied the performance of purified carbon nanotubes (P-CNTs) and polyethylene glycol carbon nanotubes (PEG-CNTs) to remove specifically chromium (Cr) and zinc (Zn) from battery wastewater by a batch adsorption process as a function of contact time, adsorbent dose and temperature. The results revealed that the optimum contact time and adsorbent dosage to remove Cr and Zn by P-CNTs and PEG-CNTs were 90 and 50 min and 0.3 g respectively. The study demonstrated that PEG-CNTs performed better compared to P-CNTs. E. M. Elsehly *et al.*<sup>207</sup> reported the use of functionalized carbon nanotubes for fabrication of filters to remove chromium from aqueous solutions. Removal of heavy metals from water by using multistage functionalized multiwall carbon nanotubes has been reported by D. Budimirović *et al.*<sup>208</sup> In a recent report by M. M. Aslam *et al.*<sup>209</sup> the preparation and application of f-CNTs for water and wastewater treatment have been reviewed. It was observed that, functionalized CNTs have proven to be a promising nanomaterial for the decontamination of water particularly due to their high adsorption capacity. A. A. Atiyah *et al.*<sup>210</sup> reported excellent antibacterial activity of silver nanoparticle deposited MWCNTs against two pathogenic bacteria, *Pseudomonas aeruginosa* and *Staphylococcus aureus*. Recently S. M. Al-Hakami *et al.*<sup>211</sup> reported the use of microwave irradiated 1-octadecanol (C18) functionalized CNTs for removal of *Escherichia coli* (*E. coli*) from water. They observed that microwave irradiated unmodified CNTs removed only up to 98% of bacteria from water, while CNTs-C18 were able to remove up to 100% of bacteria under similar conditions.

#### 4.4 Drug delivery system

Functionalized nanotubes have emerged as a novel and versatile drug delivery vehicles due to their high drug loading efficiency along with an ultrahigh surface area.<sup>212</sup> S. Sharma *et al.* studied the effect of functionalization on the drug delivery potential of CNTs where the results showed extended resistance time with a sustained release profile for drug loaded surface engineered MWCNTs.<sup>213</sup> S. Prakash *et al.* reviewed the use of f-CNTs as drug delivery vehicles in relation to cancer therapy.<sup>214</sup> C. L. Lay *et al.* also studied the use of f-CNTs for anticancer drug delivery. They reported that the most widely adopted species for functionalization is poly(ethylene glycol), which enhances the

biocompatibility and dispersability of CNTs in aqueous solution. Treatment efficacy of f-CNTs loaded with anticancer drugs, such as doxorubicin, and paclitaxel was studied both by *in vitro* and *in vivo* techniques. The results demonstrated that f-CNTs were promising for development of unique delivery systems for anticancer drugs.<sup>215</sup> J. M. Tan *et al.*<sup>216</sup> reviewed the biocompatibility of f-CNTs in designing drug delivery systems, where drug release from CNTs was achieved by utilizing various stimulants such as magnetic or electric field and changes in pH. They have discussed various parameters responsible for achieving higher therapeutic efficiency of targeted drug delivery. Recently, S. Paliwal *et al.*,<sup>217</sup> reviewed f-CNTs as a nano carrier drug delivery system.

Molecular modeling studies have also been performed to gain a mechanistic understanding of surface functionalization of carbon nanotubes as a nanocarrier with cladribine anticancer drug.<sup>218</sup> Studies have been conducted by means of density functional theory and molecular dynamics simulation calculations to investigate the drug delivery performance of the functionalized SWCNTs with a carboxylic acid group for flutamide anticancer drug in the gas phase as well as water solution.<sup>219</sup> A. A. Bhirde *et al.*<sup>220</sup> studied the distribution and clearance of polyethylene glycol (PEG)-SWCNTs as drug delivery vehicles for the anticancer drug cisplatin, where tumor growth inhibition was studied in mice. The studies revealed that control SWCNTs were lodged in lung tissues as large aggregates compared to PEG-SWCNTs, which showed little or no accumulation. J. Chen *et al.*<sup>32</sup> studied the use of f-SWCNTs as a vehicle for tumor-targeted drug delivery. The results showed high potency of material towards specific cancer cell lines. In a recent review, J. Jampilek *et al.*<sup>221</sup> summarized the latest designed nanosystems based on functionalized graphene and carbon nanotubes mainly for anticancer therapy.

## 5. Future recommendations

Functionalization of CNTs has allowed the drawbacks associated with pristine CNTs<sup>222,223</sup> to be overcome as well as tuning their properties for specific applications.<sup>224-230</sup> Further, the availability of a wide variety of functionalization approaches discussed in this article gives an opportunity for judicious selection of a particular method resulting in required functionality and performance. Not only have functional groups been added to the surface and tips of CNTs, but these unique nanomaterials have been used as a carrier vehicle loaded with a variety of biological molecules and drugs for their targeted delivery to any organ of the human body. As the application of f-CNTs in different areas is increasing, hazards due to their exposure to both humans and the environment are also increasing. Although a lot of studies have been carried out from time to time drawing the attention of the scientific community towards unexplored drawbacks and risks associated with this material,<sup>205,231-237</sup> still deeper understanding of their harm to the environment and human body is urgently required.

In this respect a variety of novel functional groups are being reported by different researchers for tackling the biocompatibility issue. Such groups may be incorporated to functionalize



carbon nanotubes in order to enhance their biocompatibility. A massive amount of work has been done on the functional properties of f-CNTs, which beyond doubt enhances the applicability of this material. However, an additional volume of work is yet to be undertaken for making this material bio-friendly and environment friendly. To decrease the toxicity concern of f-CNTs, computational tools can also be employed such as Autodock, Gaussian, *etc.* These tools along with their experimental validation may render this material a well accepted functional material.

## 6. Conclusion

CNTs have attracted attention of the scientific community due to their unique properties and wide application in the various areas of science and technology. But they also have some disadvantages preventing them being ideal materials for proposed applications. The primary one is the cost. Conventionally they are synthesized by different methods especially by arc discharge, laser vaporization and CVD. But now various modifications of these technique and also new techniques have emerged, which lower the cost considerably. On the other hand raw carbon nanotubes contain impurities such as metal nanoparticles and amorphous carbon which are to be removed by treatment with strong acids and oxidizing agents. The purified CNTs are inert and tend to agglomerate due to strong van der Waals forces and hence the dispersion and the reinforcing effect get suppressed. To overcome the aggregation and to increase dispersion, functionalization is needed. Different covalent and non covalent exohedral and endohedral functionalization techniques are used to improve their functional properties. The functionalized CNTs provide possibility of further chemical derivatization and thus have a greater versatility for applications of CNTs in different areas such as materials science, biomedical science and water purification. Functionalized carbon nanotubes have been widely studied and successfully used as adsorbents for removal of toxic contaminants such as chromium, arsenic, zinc, *etc.* along with liquid contaminants such as oils and organic solvents. They have been used for fabrication of ultra and nano filtration membranes for desalination application. Functionalized carbon nanotubes have also been used for water disinfection by removal of pathogenic microorganisms from water. Functionalized CNTs are also useful for delivery of drugs in solid tumors, and cancer and a plethora of other biomedical applications.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors wish to express their gratitude to the Director Dr Sanjai Kumar Dwivedi, Defence Research Laboratory for giving permission to publish this review article.

## References

- 1 S. Iijima, *Nature*, 1991, **354**, 56–58.
- 2 B. T. Yermagambet, M. K. Kazankapova, Z. M. Kassenova and A. T. Nauryzbayeva, *Number*, 2020, **5**, 126–133.
- 3 K. K. Singh, S. K. Chaudhary, R. Venugopal and A. Gaurav, *Proc. Inst. Mech. Eng., Part N*, 2017, **231**, 141–151.
- 4 K. Anazawa, K. Shimotani, C. Manabe, H. Watanabe and M. Shimizu, *Appl. Phys. Lett.*, 2002, **81**, 739–741.
- 5 Z. Shi, Y. Lian, F. H. Liao, X. Zhou, Z. Gu, Y. Zhang, S. Iijima, H. Li, K. T. Yue and S. L. Zhang, *J. Phys. Chem. Solids*, 2000, **61**, 1031–1036.
- 6 C. Journet, W. K. Maser, P. Bernier, A. Loiseau, M. Lamy de la Chapelle, S. Lefrant, P. Deniard, R. Lee and J. E. Fischer, *Nature*, 1997, **388**, 756–758.
- 7 X. Sun, W. Bao, Y. Lv, J. Deng and X. Wang, *Mater. Lett.*, 2007, **61**, 3956–3958.
- 8 S. Arepalli, *J. Nanosci. Nanotechnol.*, 2004, **4**, 317–325.
- 9 M. S. Hasnain and A. K. Nayak, in *SpringerBriefs in Applied Sciences and Technology*, Springer Verlag, 2019, pp. 17–20.
- 10 B. Verma, H. Sewani and C. Balomajumder, *Environ. Sci. Pollut. Res.*, 2020, **27**, 14007–14018.
- 11 C. J. Lee, J. H. Park and J. Park, *Chem. Phys. Lett.*, 2000, **323**, 560–565.
- 12 W. Z. Li, D. Z. Wang, S. X. Yang, J. G. Wen and Z. F. Ren, *Chem. Phys. Lett.*, 2001, **335**, 141–149.
- 13 Y. F. Zhang, Y. H. Tang, Y. Zhang, C. S. Lee, I. Bello and S. T. Lee, *Chem. Phys. Lett.*, 2000, **330**, 48–52.
- 14 M. Su, B. Zheng and J. Liu, *Chem. Phys. Lett.*, 2000, **322**, 321–326.
- 15 O. Noury, T. Stoöckli, M. Croci and A. Chaätelain Jean-Marc Bonard, *Chem. Phys. Lett.*, 2001, **346**, 349–355.
- 16 R. S. Rajaura, I. Singhal, K. N. Sharma and S. Srivastava, *Rev. Sci. Instrum.*, 2019, **90**, 123903.
- 17 P. Nikolaev, M. J. Bronikowski, R. K. Bradley, F. Rohmund, D. T. Colbert, K. A. Smith and R. E. Smalley, *Chem. Phys. Lett.*, 1999, **313**, 91–97.
- 18 R. L. Vander Wal, G. M. Berger and L. J. Hall, *J. Phys. Chem. B*, 2002, **106**, 3564–3567.
- 19 D. Huličová, K. Hosoi, S. -I. Kuroda, H. Abe and A. Oya, *Adv. Mater.*, 2002, **14**, 452–455.
- 20 K. Edgar and J. L. Spencer, *Curr. Appl. Phys.*, 2004, **4**, 121–124.
- 21 R. C. Z. Lofrano, J. M. Rosolen and L. A. Montoro, *Carbon*, 2005, **43**, 200.
- 22 M. Shao, D. Wang, G. Yu, B. Hu, W. Yu and Y. Qian, *Carbon*, 2004, **42**, 183–185.
- 23 M. wei Li, Z. Hu, X. zhang Wang, Q. Wu, Y. Chen and Y. L. Tian, *Diam. Relat. Mater.*, 2004, **13**, 111–115.
- 24 Y. L. Li, I. A. Kinloch, M. S. P. Shaffer, J. Geng, B. Johnson and A. H. Windle, *Chem. Phys. Lett.*, 2004, **384**, 98–102.
- 25 S. R. C. Vivekchand, L. M. Cele, F. L. Deepak, A. R. Raju and A. Govindaraj, *Chem. Phys. Lett.*, 2004, **386**, 313–318.
- 26 D. H. Robertson, D. W. Brenner and J. W. Mintmire, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1992, **45**, 12592–12595.
- 27 M. F. Yu, B. S. Files, S. Arepalli and R. S. Ruoff, *Phys. Rev. Lett.*, 2000, **84**, 5552–5555.
- 28 B. I. Yakobson, C. J. Brabec and J. Bernholc, *Phys. Rev. Lett.*, 1996, **76**, 2511–2514.



- 29 S. J. Tans, A. R. M. Verschueren and C. Dekker, *Nature*, 1998, **393**, 49–52.
- 30 B. Q. Wei, R. Vajtai and P. M. Ajayan, *Appl. Phys. Lett.*, 2001, **79**, 1172–1174.
- 31 J. Hone, M. C. Llaguno, M. J. Biercuk, A. T. Johnson, B. Batlogg, Z. Benes and J. E. Fischer, *Appl. Phys. Mater. Sci. Process*, 2002, **74**, 339–343.
- 32 J. Chen, S. Chen, X. Zhao, L. V. Kuznetsova, S. S. Wong and I. Ojima, *J. Am. Chem. Soc.*, 2008, **130**, 16778–16785.
- 33 F. Ito, K. Konuma and A. Okamoto, *J. Appl. Phys.*, 2001, **89**, 8141–8145.
- 34 P. Avouris, *Acc. Chem. Res.*, 2002, **35**, 1026–1034.
- 35 B. Safadi, R. Andrews and E. A. Grulke, *J. Appl. Polym. Sci.*, 2002, **84**, 2660–2669.
- 36 S. Fan, M. G. Chapline, N. R. Franklin, T. W. Tombler, A. M. Cassell and H. Dai, *Science*, 1999, **283**, 512–514.
- 37 Q. H. Wang, A. A. Setlur, J. M. Lauerhaas, J. Y. Dai, E. W. Seelig and R. P. H. Chang, *Appl. Phys. Lett.*, 1998, **72**, 2912–2913.
- 38 A. C. Dillon, K. M. Jones, T. A. Bekkedahl, C. H. Kiang, D. S. Bethune and M. J. Heben, *Nature*, 1997, **386**, 377–379.
- 39 S. Mudassir Ali, K. Venkateswara Rao, J. V. Ramana Rao, V. Himabindu, M. Venkateswara Rao and V. Viditha, in *Proceedings of the International Conference on Nanoscience, Engineering and Technology*, ICONSET, 2011, pp. 1–4.
- 40 L. Moreira, R. Fulchiron, G. Seytre, P. Dubois and P. Cassagnau, *Macromolecules*, 2010, **43**, 1467–1472.
- 41 Q. Chen, C. Saliel, S. Manickavasagam, L. S. Schadler, R. W. Siegel and H. Yang, *J. Colloid Interface Sci.*, 2004, **280**, 91–97.
- 42 C. A. Dyke and J. M. Tour, *Chem.–Eur. J.*, 2004, **10**, 812–817.
- 43 J. Zhu, J. D. Kim, H. Peng, J. L. Margrave, V. N. Khabashesku and E. V. Barrera, *Nano Lett.*, 2003, **3**, 1107–1113.
- 44 Q. S. Yang, B. Q. Li, X. Q. He and Y. W. Mai, *Adv. Condens. Matter Phys.*, 2014, **2014**, 1–8.
- 45 M. Noordadi, F. Mehrnejad, R. H. Sajedi, M. Jafari and B. Ranjbar, *PLoS One*, 2018, **13**, e0198519.
- 46 P. Wolski, K. Nieszporek and T. Panczyk, *Phys. Chem. Chem. Phys.*, 2017, **19**, 9300–9312.
- 47 S. Merum, J. B. Veluru and R. Seeram, *Mater. Sci. Eng., B*, 2017, **223**, 43–63.
- 48 B. V. Basheer, J. J. George, S. Siengchin and J. Parameswaranpillai, *Nano-Struct. Nano-Objects*, 2020, **22**, 100429.
- 49 R. Alshehri, A. M. Ilyas, A. Hasan, A. Arnaout, F. Ahmed and A. Memic, *J. Med. Chem.*, 2016, **59**, 8149–8167.
- 50 S. Beg, M. Rahman, A. Jain, S. Saini, M. S. Hasnain, S. Swain, S. Imam, I. Kazmi and S. Akhter, in *Fullerenes, Graphenes and Nanotubes*, Elsevier, 2018, pp. 105–133.
- 51 C. Pennetta, G. Floresta, A. C. E. Graziano, V. Cardile, L. Rubino, M. Galimberti, A. Rescifina and V. Barbera, *Nanomaterials*, 2020, **10**, 1073.
- 52 A. A. Farghali, H. A. Abdel Tawab, S. A. Abdel Moaty and R. Khaled, *J. Nanostructure Chem.*, 2017, **7**, 101–111.
- 53 S. Ali, S. A. U. Rehman, H.-Y. Luan, M. U. Farid and H. Huang, *Sci. Total Environ.*, 2019, **646**, 1126–1139.
- 54 A. J. Haider, T. R. Marzoog, I. H. Hadi and Z. N. Jameel, *J. Environ. Manage.*, 2018, **246**, 030013.
- 55 L. Ma, X. Dong, M. Chen, L. Zhu, C. Wang, F. Yang and Y. Dong, *Membranes*, 2017, **7**, 16.
- 56 E. T. Mickelson, C. B. Huffman, A. G. Rinzler, R. E. Smalley, R. H. Hauge and J. L. Margrave, *Chem. Phys. Lett.*, 1998, **296**, 188–194.
- 57 E. T. Mickelson, I. W. Chiang, J. L. Zimmerman, P. J. Boul, J. Lozano, J. Liu, R. E. Smalley, R. H. Hauge and J. L. Margrave, *J. Phys. Chem. B*, 1999, **103**, 4318–4322.
- 58 V. N. Khabashesku, W. E. Billups and J. L. Margrave, *Acc. Chem. Res.*, 2002, **35**, 1087–1095.
- 59 P. J. Boul, J. Liu, E. T. Mickelson, C. B. Huffman, L. M. Ericson, I. W. Chiang, K. A. Smith, D. T. Colbert, R. H. Hauge, J. L. Margrave and R. E. Smalley, *Chem. Phys. Lett.*, 1999, **310**, 367–372.
- 60 S. Pekker, J. P. Salvetat, E. Jakab, J. M. Bonard and L. Forró, *J. Phys. Chem. B*, 2001, **105**, 7938–7943.
- 61 B. N. Khare, M. Meyyappan, A. M. Cassell, C. V. Nguyen and J. Han, *Nano Lett.*, 2002, **2**, 73–77.
- 62 N. Tagmatarchis and M. Prato, *J. Mater. Chem.*, 2004, **14**, 437.
- 63 V. Georgakilas, K. Kordatos, M. Prato, D. M. Guldi, M. Holzinger and A. Hirsch, *J. Am. Chem. Soc.*, 2002, **124**, 760–761.
- 64 J. L. Bahr, J. Yang, D. V. Kosynkin, M. J. Bronikowski, R. E. Smalley and J. M. Tour, *J. Am. Chem. Soc.*, 2001, **123**, 6536–6542.
- 65 J. L. Bahr and J. M. Tour, *Chem. Mater.*, 2001, **13**, 3823–3824.
- 66 F. J. M. Holzinger, O. Vostrowsky, A. Hirsch, M. Kappes and R. Weiss, *Angew. Chem., Int. Ed.*, 2001, **40**, 4002–4005.
- 67 M. Holzinger, J. Abraham, P. Whelan, R. Graupner, L. Ley, F. Hennrich, M. Kappes and A. Hirsch, *J. Am. Chem. Soc.*, 2003, **125**, 8566–8580.
- 68 Y. Ying, R. K. Saini, F. Liang, A. K. Sadana and W. E. Billups, *Org. Lett.*, 2003, **5**, 1471–1473.
- 69 N. Tagmatarchis, V. Georgakilas, M. Prato and H. Shinohara, *Chem. Commun.*, 2002, **2**, 2010–2011.
- 70 S. Banerjee and S. S. Wong, *Nano Lett.*, 2002, **2**, 49–53.
- 71 S. Banerjee and S. S. Wong, *J. Am. Chem. Soc.*, 2002, **124**, 8940–8948.
- 72 P. X. Hou, S. Bai, Q. H. Yang, C. Liu and H. M. Cheng, *Carbon*, 2002, **40**, 81–85.
- 73 H. Hiura, T. W. Ebbesen and K. Tanigaki, *Adv. Mater.*, 1995, **7**, 275–276.
- 74 S. C. Tsang, Y. K. Chen, P. J. F. Harris and M. L. H. Green, *Nature*, 1994, **372**, 159–162.
- 75 R. M. Lago, S. C. Tsang, K. L. Lu, Y. K. Chen and M. L. H. Green, *J. Chem. Soc., Chem. Commun.*, 1995, 1355–1356.
- 76 K. C. Hwang, *J. Chem. Soc., Chem. Commun.*, 1995, 173–174.
- 77 S. R. P. W. Chiu, G. S. Duesberg and U. D. Weglikowska, *Appl. Phys. Lett.*, 2002, **80**, 3811–3813.
- 78 N. Zhang, J. Xie and V. K. Varadan, *Smart Mater. Struct.*, 2002, **11**, 962.



- 79 V. Datsyuk, M. Kalyva, K. Papagelis, J. Parthenios, D. Tasis, A. Siokou, I. Kallitsis and C. Galiotis, *Carbon*, 2008, **46**, 833–840.
- 80 S. Liang, G. Li and R. Tian, *J. Mater. Sci.*, 2016, **51**, 3513–3524.
- 81 M. A. Hamon, J. Chen, H. Hu, Y. Chen, M. E. Itkis, A. M. Rao, P. C. Eklund and R. C. Haddon, *Adv. Mater.*, 1999, **11**, 834–840.
- 82 S. Niyogi, M. A. Hamon, H. Hu, B. Zhao, P. Bhowmik, R. Sen, M. E. Itkis and R. C. Haddon, *Acc. Chem. Res.*, 2002, **35**, 1105–1113.
- 83 Y. P. Sun, W. Huang, Y. Lin, K. Fu, A. Kitaygorodskiy, L. A. Riddle, Y. J. Yu and D. L. Carroll, *Chem. Mater.*, 2001, **13**, 2864–2869.
- 84 K. Fu, W. Huang, Y. Lin, L. A. Riddle, D. L. Carroll and Y. P. Sun, *Nano Lett.*, 2001, **1**, 439–441.
- 85 Y. P. Sun, K. Fu, Y. Lin and W. Huang, *Acc. Chem. Res.*, 2002, **35**, 1096–1104.
- 86 F. Pompeo and D. E. Resasco, *Nano Lett.*, 2002, **2**, 369–373.
- 87 J. Chen, A. M. Rao, S. Lyuksyutov, M. E. Itkis, M. A. Hamon, H. Hu, R. W. Cohn, P. C. Eklund, D. T. Colbert, R. E. Smalley and R. C. Haddon, *J. Phys. Chem. B*, 2001, **105**, 2525–2528.
- 88 M. F. Variava, T. L. Church, A. T. Harris and A. I. Minett, *J. Mater. Chem. A*, 2013, **1**, 8509.
- 89 V. Lordi, N. Yao and J. Wei, *Chem. Mater.*, 2001, **13**, 733–737.
- 90 R. Yu, L. Chen, Q. Liu, J. Lin, K. L. Tan, S. C. Ng, H. S. O. Chan, G. Q. Xu and T. S. A. Hor, *Chem. Mater.*, 1998, **10**, 718–722.
- 91 W. Zhang, J. Chen, G. F. Swiegers, Z.-F. Ma and G. G. Wallace, *Nanoscale*, 2010, **2**, 282–286.
- 92 L. Li and Y. Xing, *J. Phys. Chem. C*, 2007, **111**, 2803–2808.
- 93 M. M. Waje, X. Wang, W. Li and Y. Yan, *Nanotechnology*, 2005, **16**, S395–S400.
- 94 J. Shi, Z. Wang and H. L. Li, *J. Nanoparticle Res.*, 2006, **8**, 743–747.
- 95 A. Muhammad, N. A. Yusof, R. Hajian and J. Abdullah, *J. Mater. Res.*, 2016, **31**, 2897–2905.
- 96 K. Jiang, A. Eitan, L. S. Schadler, P. M. Ajayan, R. W. Siegel, N. Grobert, M. Mayne, M. Reyes-Reyes, H. Terrones and M. Terrones, *Nano Lett.*, 2003, **3**, 275–277.
- 97 A. V. Ellis, K. Vijayamohan, R. Goswami, N. Chakrapani, L. S. Ramanathan, P. M. Ajayan and G. Ramanath, *Nano Lett.*, 2003, **3**, 279–282.
- 98 G. L. Hwang, K. C. Hwang, Y. T. Shieh and S. J. Lin, *Chem. Mater.*, 2003, **15**, 1353–1357.
- 99 N. Sarlak, M. Adeli, M. Karimi, M. Bordbare and M. A. Farahmandnejad, *J. Mol. Liq.*, 2013, **180**, 39–44.
- 100 Y. Zhou, Y. Fang and R. Ramasamy, *Sensors*, 2019, **19**, 392.
- 101 N. Kocharova, T. Ääritalo, J. Leiro, J. Kankare and J. Lukkari, *Langmuir*, 2007, **23**, 3363–3371.
- 102 C. Hu, H. Liao, F. Li, J. Xiang, W. Li, S. Duo and M. Li, *Mater. Lett.*, 2008, **62**(17–18), 2585–2588.
- 103 B. R. Priya and H. J. Byrne, *J. Phys. Chem. C*, 2008, **112**, 332–337.
- 104 B. White, S. Banerjee, S. O'Brien, N. J. Turro and I. P. Herman, *J. Phys. Chem. C*, 2007, **111**, 13684–13690.
- 105 T. J. McDonald, C. Engtrakul, M. Jones, G. Rumbles and M. J. Heben, *J. Phys. Chem. B*, 2006, **110**, 25339–25346.
- 106 D. A. Britz and A. N. Khlobystov, *Chem. Soc. Rev.*, 2006, **35**, 637–659.
- 107 H. Cui, X. Yan, M. Monasterio and F. Xing, *Nanomaterials*, 2017, **7**, 262.
- 108 M. F. Islam, E. Rojas, D. M. Bergey, A. T. Johnson and A. G. Yodh, *Nano Lett.*, 2003, **3**, 269–273.
- 109 R. Shvartzman-Cohen, Y. Levi-Kalisman, E. Nativ-Roth and R. Yerushalmi-Rozen, *Langmuir*, 2004, **20**, 6085–6088.
- 110 O. V. Kharissova, B. I. Kharisov and E. G. de Casas Ortiz, *RSC Adv.*, 2013, **3**, 24812.
- 111 J. Rausch, R.-C. Zhuang and E. Mäder, *Compos. Appl. Sci. Manuf.*, 2010, **41**, 1038–1046.
- 112 Y. Shi, L. Ren, D. Li, H. Gao and B. Yang, *J. Surf. Eng. Mater. Adv. Technol.*, 2013, **03**, 6–12.
- 113 L. Jiang, L. Gao and J. Sun, *J. Colloid Interface Sci.*, 2003, **260**, 89–94.
- 114 D. Yin, P. Luo, J. Zhang, X. Yao, R. Wang, L. Wang and S. Wang, *Appl. Sci.*, 2019, **9**, 497.
- 115 M. J. O'Connell, P. Boul, L. M. Ericson, C. Huffman, Y. Wang, E. Haroz, C. Kuper, J. Tour, K. D. Ausman and R. E. Smalley, *Chem. Phys. Lett.*, 2001, **342**, 265–271.
- 116 T. Fujigaya and N. Nakashima, *Sci. Technol. Adv. Mater.*, 2015, **16**, 024802.
- 117 S. H. Tan, J. C. Goak, N. Lee, J.-Y. Kim and S. C. Hong, *Macromol. Symp.*, 2007, **249–250**, 270–275.
- 118 M. Zheng, A. Jagota, E. D. Semke, B. A. Diner, R. S. McLean, S. R. Lustig, R. E. Richardson and N. G. Tassi, *Nat. Mater.*, 2003, **2**, 338–342.
- 119 D. W. Steuerman, A. Star, R. Narizzano, H. Choi, R. S. Ries, C. Nicolini, J. F. Stoddart and J. R. Heath, *J. Phys. Chem. B*, 2002, **106**, 3124–3130.
- 120 A. Star, Y. Liu, K. Grant, L. Ridvan, J. F. Stoddart, D. W. Steuerman, M. R. Diehl, A. Boukai and J. R. Heath, *Macromolecules*, 2003, **36**, 553–560.
- 121 B. Z. Tang and H. Xu, *Macromolecules*, 1999, **32**, 2569–2576.
- 122 K. A. S. Fernando, Y. Lin, W. Wang, S. Kumar, B. Zhou, S. Y. Xie, L. S. T. Cureton and Y. P. Sun, *J. Am. Chem. Soc.*, 2004, **126**, 10234–10235.
- 123 R. J. Chen, Y. Zhang, D. Wang and H. Dai, *J. Am. Chem. Soc.*, 2001, **123**, 3838–3839.
- 124 H. Murakami, T. Nomura and N. Nakashima, *Chem. Phys. Lett.*, 2003, **378**, 481–485.
- 125 H. Xia, Q. Wang and G. Qiu, *Chem. Mater.*, 2003, **15**, 3879–3886.
- 126 Y. Kang and T. A. Taton, *J. Am. Chem. Soc.*, 2003, **125**, 5650–5651.
- 127 W. Zhou, S. Lv and W. Shi, *Eur. Polym. J.*, 2008, **44**, 587–601.
- 128 M. S. Arnold, M. O. Guler, M. C. Hersam and S. I. Stupp, *Langmuir*, 2005, **21**, 4705–4709.
- 129 S. J. Pastine, D. Okawa, A. Zettl and J. M. J. Fréchet, *J. Am. Chem. Soc.*, 2009, **131**, 13586–13587.
- 130 L. Qu and L. Dai, *J. Am. Chem. Soc.*, 2005, **127**, 10806–10807.
- 131 H. C. Choi, M. Shim, S. Bangsaruntip and H. Dai, *J. Am. Chem. Soc.*, 2002, **124**, 9058–9059.



- 132 B. M. Quinn, C. Dekker and S. G. Lemay, *J. Am. Chem. Soc.*, 2005, **127**, 6146–6147.
- 133 P. J. Li, Y. Chai, X. L. Zhou, Q. F. Zhang and J. L. Wu, *Fullerenes, Nanotub. Carbon Nanostruct.*, 2005, **13**, 377–383.
- 134 Y. Zhang, N. W. Franklin, R. J. Chen and H. Dai, *Chem. Phys. Lett.*, 2000, **331**, 35–41.
- 135 K. Pichler, H. Kuzmany, H. Kataura and Y. Achiba, *Phys. Rev. Lett.*, 2001, **87**, 267401–267404.
- 136 M. W. Maddox and K. E. Gubbins, *J. Chem. Phys.*, 1997, **107**, 9659–9667.
- 137 G. Stan and M. W. Cole, *Surf. Sci.*, 1998, **395**, 280–291.
- 138 X. Huang, H. Yu, H. Tan, J. Zhu, W. Zhang, C. Wang, J. Zhang, Y. Wang, Y. Lv, Z. Zeng, D. Liu, J. Ding, Q. Zhang, M. Srinivasan, P. M. Ajayan, H. H. Hng and Q. Yan, *Adv. Funct. Mater.*, 2014, **24**, 6516–6523.
- 139 T. Cui, X. Pan, J. Dong, S. Miao, D. Miao and X. Bao, *Nano Res.*, 2018, **11**, 3132–3144.
- 140 C. Guerret-Piécourt, Y. Le Bouar, A. Lolseau and H. Pascard, *Nature*, 1994, **372**, 761–765.
- 141 H. H. P. M. Ajayan, T. W. Ebbesen, T. Ichihashi, S. Iijima and K. Tanigaki, *Nature*, 1993, **362**, 522–525.
- 142 E. Dujardin, T. W. Ebbesen, H. Hiura and K. Tanigaki, *Science*, 1994, **265**, 1850–1852.
- 143 B. W. Smith, M. Monthieux and D. E. Luzzi, *Chem. Phys. Lett.*, 1999, **315**, 31–36.
- 144 B. W. Smith and D. E. Luzzi, *Chem. Phys. Lett.*, 2000, **321**, 169–174.
- 145 G. H. Jeong, T. Hirata, R. Hatakeyama, K. Tohji and K. Motomiya, *Carbon*, 2002, **40**, 2247–2253.
- 146 H. Kataura, Y. Maniwa, T. Kodama, K. Kikuchi, K. Hirahara, K. Suenaga, S. Iijima, S. Suzuki, Y. Achiba and W. Krätschmer, *Synth. Met.*, 2001, **121**, 1195–1196.
- 147 F. d B. Mota, E. F. Almeida Júnior and C. M. C. de Castilho, *Braz. J. Phys.*, 2008, **38**, 70–73.
- 148 D. E. Luzzi and B. W. Smith, *Carbon*, 2000, **38**, 1751–1756.
- 149 J. Sloan, R. E. Dunin-Borkowski, J. L. Hutchison, K. S. Coleman, V. Clifford Williams, J. B. Claridge, A. P. E. York, C. Xu, S. R. Bailey, G. Brown, S. Friedrichs and M. L. H. Green, *Chem. Phys. Lett.*, 2000, **316**(3–4), 191–198.
- 150 S. Bandow, M. Takizawa, K. Hirahara, M. Yudasaka and S. Iijima, *Chem. Phys. Lett.*, 2001, **337**, 48–54.
- 151 T. Okazaki, K. Suenaga, K. Hirahara, S. Bandow, S. Iijima and H. Shinohara, *Phys. B Condens. Matter*, 2002, **323**, 97–99.
- 152 C. S. Allen, Y. Ito, A. W. Robertson, H. Shinohara and J. H. Warner, *ACS Nano*, 2011, **5**, 10084–10089.
- 153 K. Hirahara, K. Suenaga, S. Bandow, H. Kato, T. Okazaki, H. Shinohara and S. Iijima, *Phys. Rev. Lett.*, 2000, **85**, 5384–5387.
- 154 D. E. Luzzi and B. W. Smith, in *Science and Application of Nanotubes*, Kluwer Academic Publishers, 2005, pp. 67–76.
- 155 B. Bouteaux, A. Claye, B. W. Smith, M. Monthieux, D. E. Luzzi and J. E. Fischer, *Chem. Phys. Lett.*, 1999, **310**, 21–24.
- 156 L. Grigorian, K. A. Williams, S. Fang, G. U. Sumanasekera, A. L. Loper, E. C. Dickey, S. J. Pennycook and P. C. Eklund, *Phys. Rev. Lett.*, 1998, **80**, 5560–5563.
- 157 X. Fan, E. C. Dickey, P. C. Eklund, K. A. Williams, L. Grigorian, R. Buczko, S. T. Pantelides and S. J. Pennycook, *Phys. Rev. Lett.*, 2000, **84**, 4621–4624.
- 158 A. M. Díez-Pascual, *Macromol*, 2021, **1**, 64–83.
- 159 S. T. R. Naqvi, T. Rasheed, D. Hussain, M. Najam ul Haq, S. Majeed, S. shafi, N. Ahmed and R. Nawaz, *J. Mol. Liq.*, 2020, **297**, 111919.
- 160 R. Soleyman, S. Hirbod and M. Adeli, *Biomater. Sci.*, 2015, **3**, 695–711.
- 161 T. P. Dyachkova, D. V. Tarov, E. A. Burakova, E. N. Tugolukov, A. N. Blokhin, E. V. Galunin, L. V. Rosenblum and D. E. Kobzev, in *IOP Conference Series: Materials Science and Engineering*, IOP Publishing Ltd, 2019, vol. 693, p. 012011.
- 162 M. L. Shofner, V. N. Khabashesku and E. V. Barrera, *Chem. Mater.*, 2006, **18**, 906–913.
- 163 S. W. Kim, T. Kim, Y. S. Kim, H. S. Choi, H. J. Lim, S. J. Yang and C. R. Park, *Carbon*, 2012, **50**, 3–33.
- 164 C. A. Mitchell, J. L. Bahr, S. Arepalli, J. M. Tour and R. Krishnamoorti, *Macromolecules*, 2002, **35**, 8825–8830.
- 165 H. J. Barraza, F. Pompeo, E. A. O'Rear and D. E. Resasco, *Nano Lett.*, 2002, **2**(8), 797–802.
- 166 A. H. Labulo, B. S. Martincigh, B. Omondi and V. O. Nyamori, *J. Mater. Sci.*, 2017, **52**, 9225–9248.
- 167 B. Ye, S. I. Kim, M. Lee, M. Ezazi, H. D. Kim, G. Kwon and D. H. Lee, *RSC Adv.*, 2020, **10**, 16700–16708.
- 168 M. Melchionna, S. Marchesan, M. Prato and P. Fornasiero, *Catalysis Science and Technology*, 2013, (1–3), 1–16.
- 169 J. P. Tessonnier, L. Pesant, G. Ehret, M. J. Ledoux and C. Pham-Huu, *Appl. Catal. Gen.*, 2005, **288**, 203–210.
- 170 J. John, E. Gravel, I. N. N. Namboothiri and E. Doris, *Nanotechnol. Rev.*, 2012, **1**, 515–539.
- 171 N. Coustel, B. Coq, V. Brotons, P. S. Kumbhar, R. Dutartre, P. Geneste, J. M. Planeix, P. Bernier and P. M. Ajayan, *J. Am. Chem. Soc.*, 1994, **116**, 7935–7936.
- 172 B. Wu, Y. Kuang, X. Zhang and J. Chen, *Nano Today*, 2011, **6**, 75–90.
- 173 Q. Wang, N. Dai, J. Zheng and J. P. Zheng, *J. Electroanal. Chem.*, 2019, **854**, 113508.
- 174 W. Li, C. Gao, H. Qian, J. Ren and D. Yan, *J. Mater. Chem.*, 2006, **16**, 1852–1859.
- 175 H. Lin, H. Zhu, H. Guo and L. Yu, *Mater. Lett.*, 2007, **61**, 3547–3550.
- 176 D. W. X. Gui, W. Ye, J. Wei, K. Wang, R. Lv, H. Zhu, F. Kang and J. Gu, *J. Phys. D*, 2009, **42**, 75002–75005.
- 177 Z. Guo, P. J. Sadler and S. C. Tsang, *Adv. Mater.*, 1998, **10**, 701–703.
- 178 F. Balavoine, P. Schultz, C. Richard, V. Mallouh, T. W. Ebbesen and C. Mioskowski, *Angew. Chem., Int. Ed.*, 1999, **38**, 1912–1915.
- 179 S. C. Tsang, Z. Guo, Y. K. Chen, M. L. H. Green, H. A. O. Hill, T. W. Hambley and P. J. Sadler, *Angew. Chem., Int. Ed.*, 1997, **36**, 2198–2200.



- 180 H. Maruyama and Y. Nakayama, *Appl. Phys. Express*, 2008, **1**, 1240011–1240013.
- 181 R. J. Chen, Y. Zhang, D. Wang and H. Dai, *J. Am. Chem. Soc.*, 2001, **123**, 3838–3839.
- 182 H. Hu, Y. Ni, V. Montana, R. C. Haddon and V. Parpura, *Nano Lett.*, 2004, **4**, 507–511.
- 183 K. Besteman, J. O. Lee, F. G. M. Wiertz, H. A. Heering and C. Dekker, *Nano Lett.*, 2003, **3**, 727–730.
- 184 W. Wu, S. Wiecekowsk, G. Pastorin, M. Benincasa, C. Klumpp, J.-P. Briand, R. Gennaro, M. Prato and A. Bianco, *Angew. Chem., Int. Ed.*, 2005, **44**, 6358–6362.
- 185 D. Pantarotto, C. D. Partidos, R. Graff, J. Hoebeke, J. P. Briand, M. Prato and A. Bianco, *J. Am. Chem. Soc.*, 2003, **125**, 6160–6164.
- 186 S. Wang, E. S. Humphreys, S. Y. Chung, D. F. Delduco, S. R. Lustig, H. Wang, K. N. Parker, N. W. Rizzo, S. Subramoney, Y. M. Chiang and A. Jagota, *Nat. Mater.*, 2003, **2**, 196–200.
- 187 V. Zorbas, A. Ortiz-Acevedo, A. B. Dalton, M. M. Yoshida, G. R. Dieckmann, R. K. Draper, R. H. Baughman, M. Jose-Yacamán and I. H. Musselman, *J. Am. Chem. Soc.*, 2004, **126**, 7222–7227.
- 188 M. Shim, N. W. S. Kam, R. J. Chen, Y. Li and H. Dai, *Nano Lett.*, 2002, **2**, 285–288.
- 189 T. Panczyk, P. Wojton and P. Wolski, *Int. J. Mol. Sci.*, 2020, **21**(6), 1925.
- 190 P. Wolski, P. Wojton, K. Nieszporek and T. Panczyk, *J. Phys. Chem. B*, 2019, **123**, 10343–10353.
- 191 Y. Zhang, F. Li, M. Li, X. Mao, X. Jing, X. Liu, Q. Li, J. Li, L. Wang, C. Fan and X. Zuo, *J. Am. Chem. Soc.*, 2019, **141**, 17861–17866.
- 192 K. M. Lee, C. P. P. Wong, T. L. Tan and C. W. Lai, *Mater. Sci. Eng., B*, 2018, **236–237**, 61–69.
- 193 M. Barrejón, Z. Syrgiannis, M. Burian, S. Bosi, T. Montini, P. Fornasiero, H. Amenitsch and M. Prato, *ACS Appl. Mater. Interfaces*, 2019, **11**, 12920–12930.
- 194 S. A. Jame and Z. Zhou, *Nanotechnol. Rev.*, 2016, **5**, 41–50.
- 195 S. Y. Yang, C. D. Vecitis and H. Park, *Environ. Sci. Pollut. Res.*, 2019, **26**, 1036–1043.
- 196 H. Wang, K. Y. Lin, B. Jing, G. Krylova, G. E. Sigmon, P. McGinn, Y. Zhu and C. Na, *Water Res.*, 2013, **47**, 4198–4205.
- 197 J. Liu, X. Li, W. Jia, M. Ding, Y. Zhang and S. Ren, *J. Dispersion Sci. Technol.*, 2016, **37**, 1294–1302.
- 198 N. Al-Jammal, T. A. Abdullah, T. Juzsakova, B. Zsirka, I. Cretescu, V. Vágvolgyi, V. Sebestyén, C. Le Phuoc, R. T. Rasheed and E. Domokos, *J. Environ. Chem. Eng.*, 2020, **8**, 103570.
- 199 T. A. Abdullah, T. Juzsakova, S. A. Hafad, R. T. Rasheed, N. Al-Jammal, M. A. Mallah, A. D. Salman, P. C. Le, E. Domokos and M. Aldulaimi, *Clean Technol. Environ. Policy*, 2021, **1**, 3.
- 200 Y. Hong, J. Zhang, C. Zhu, X. C. Zeng and J. S. Francisco, *J. Mater. Chem. A*, 2019, **7**, 3583–3591.
- 201 W. F. Chan, H. Y. Chen, A. Surapathi, M. G. Taylor, X. Shao, E. Marand and J. K. Johnson, *ACS Nano*, 2013, **7**, 5308–5319.
- 202 Z. Z. Chowdhury, S. Sagadevan, R. Bin Johan, S. T. Shah, A. Adebesi, S. I. Md and R. F. Rafique, *Mater. Res. Express*, 2018, **5**, 102001.
- 203 R. Das, M. E. Ali, S. B. A. Hamid, S. Ramakrishna and Z. Z. Chowdhury, *Desalination*, 2014, **336**, 97–109.
- 204 M. H. Davood, A. Farahani, D. Hua and T. S. Chung, *J. Memb. Sci.*, 2018, **548**, 319–331.
- 205 M. Sianipar, S. H. Kim, Khoiruddin, F. Iskandar and I. G. Wenten, *RSC Adv.*, 2017, **7**, 51175–51198.
- 206 W. A. Hamzat, A. S. Abdulkareem, M. T. Bankole, J. O. Tijani, A. S. Kovo and O. K. Abubakre, *J. Environ. Sci. Health, Part A: Toxic/Hazard. Subst. Environ. Eng.*, 2019, **54**, 827–839.
- 207 E. M. Elsehly, N. G. Chechenin, A. V. Makunin, H. A. Motaweh and E. G. Leksina, *Water Sci. Technol.*, 2017, **75**, 1564–1571.
- 208 D. Budimirović, Z. S. Veličković, Z. Bajić, D. L. Milošević, J. B. Nikolić, S. Drmanić and A. D. Marinković, *J. Serb. Chem. Soc.*, 2017, **82**, 1175–1191.
- 209 M. M. A. Aslam, H. W. Kuo, W. Den, M. Usman, M. Sultan and H. Ashraf, *Sustain*, 2021, **13**, 5717.
- 210 A. A. Atiyah, A. J. Haider and R. M. Dhahi, *IET Nanobiotechnol.*, 2019, **13**, 597–601.
- 211 S. M. Al-Hakami, A. B. Khalil, T. Laoui and M. A. Atieh, *Bioinorg. Chem. Appl.*, 2013, **2013**, 458943.
- 212 M. Karimi, N. Solati, M. Amiri, H. Mirshekari, E. Mohamed, M. Taheri, M. Hashemkhani, A. Saeidi, M. A. Estiar, P. Kiani, A. Ghasemi, S. M. M. Basri, A. R. Aref and M. R. Hamblin, *Expert Opin. Drug Deliv.*, 2015, **12**, 1071–1087.
- 213 S. Sharma, N. K. Mehra, K. Jain and N. K. Jain, *Artif. Cells, Nanomed. Biotechnol.*, 2016, **44**, 1851–1860.
- 214 S. Prakash, M. Malhotra, W. Shao, C. Tomaro-Duchesneau and S. Abbasi, *Adv. Drug Deliv. Rev.*, 2011, **63**, 1340–1351.
- 215 C. L. Lay, J. Liu and Y. Liu, *Expet Rev. Med. Dev.*, 2011, **8**, 561–566.
- 216 J. M. Tan, P. Arulselvan, S. Fakurazi, H. Ithnin and M. Z. Hussein, *J. Nanomater.*, 2014, **2014**, 917024.
- 217 S. Paliwal, K. Pandey, S. Pawar, H. Joshi and N. Bisht, *Indian J. Pharm. Sci.*, 2020, **82**, 766–772.
- 218 M. Lotfi, A. Morsali and M. R. Bozorgmehr, *Appl. Surf. Sci.*, 2018, **462**, 720–729.
- 219 M. Kamel, H. Raissi, A. Morsali and M. Shahabi, *Appl. Surf. Sci.*, 2018, **434**, 492–503.
- 220 A. A. Bhirde, S. Patel, A. A. Sousa, V. Patel, A. A. Molinolo, Y. Ji, R. D. Leapman, J. S. Gutkind and J. F. Rusling, *Nanomedicine*, 2010, **5**, 1535–1546.
- 221 J. Jampilek and K. Kralova, *Materials*, 2021, **14**, 1–39.
- 222 A. Bianco, K. Kostarelos and M. Prato, *Chem. Commun.*, 2011, **47**, 10182–10188.
- 223 R. Das, S. B. Abd Hamid, M. E. Ali, M. S. M. Annuar, E. M. B. Samsudin and S. Bagheri, *Sci. Adv. Mater.*, 2015, **7**, 2726–2737.
- 224 P. C. Ma, N. A. Siddiqui, G. Marom and J. K. Kim, *Compos. Appl. Sci. Manuf.*, 2010, **41**, 1345–1367.
- 225 N. J. Singhai and S. Ramteke, *Curr. Nanosci.*, 2020, **16**, 170–186.



- 226 Y. Hwang, S. H. Park and J. W. Lee, *Polymers*, 2017, **9**, 13.
- 227 Y. Zhang, Y. Bai and B. Yan, *Drug Discov. Today*, 2010, **15**, 428–435.
- 228 A. V. Liopo, M. P. Stewart, J. Hudson, J. M. Tour and T. C. Pappas, *J. Nanosci. Nanotechnol.*, 2006, **6**, 1365–1374.
- 229 G. Pastorin, *Pharm. Res.*, 2009, **26**, 746–769.
- 230 C. Ménard-Moyon, E. Venturelli, C. Fabbro, C. Samorì, T. Da Ros, K. Kostarelos, M. Prato and A. Bianco, *Expert Opin. Drug Discov.*, 2010, **5**, 691–707.
- 231 N. D. Koromilas, G. C. Lainioti, C. Gialeli, D. Barbouri, K. B. Kouravelou, N. K. Karamanos, G. A. Voyiatzis and J. K. Kallitsis, *PLoS One*, 2014, **9**, 107029.
- 232 M. Allegri, D. K. Perivoliotis, M. G. Bianchi, M. Chiu, A. Pagliaro, M. A. Koklioti, A. F. A. Trompeta, E. Bergamaschi, O. Bussolati and C. A. Charitidis, *Toxicol. Rep.*, 2016, **3**, 230–243.
- 233 D. F. Rodrigues, D. P. Jaisi and M. Elimelech, *Environ. Sci. Technol.*, 2013, **47**, 625–633.
- 234 E. Mohammadi, M. Zeinali, M. Mohammadi-Sardoo, M. Iranpour, B. Behnam and A. Mandegary, *Hum. Exp. Toxicol.*, 2020, **39**, 1147–1167.
- 235 C. L. Ursini, D. Cavallo, A. M. Fresegna, A. Ciervo, R. Maiello, S. Casciardi, F. Tombolini, G. Buresti and S. Iavicoli, *J. Nanomater.*, 2012, **2012**, 815979.
- 236 T. Coccini, E. Roda, D. A. Sarigiannis, P. Mustarelli, E. Quartarone, A. Profumo and L. Manzo, *Toxicology*, 2010, **269**, 41–53.
- 237 G. Song, X. Guo, X. Zong, L. Du, J. Zhao, C. Lai and X. Jin, *Dent. Mater. J.*, 2019, **38**, 127–135.

