Chemical Science



PERSPECTIVE

View Article Online
View Journal | View Issue



Cite this: Chem. Sci., 2023, 14, 3400

All publication charges for this article have been paid for by the Royal Society of Chemistry

Received 15th November 2022 Accepted 8th January 2023

DOI: 10.1039/d2sc06298d

rsc.li/chemical-science

Insights into alloy/oxide or hydroxide interfaces in Ni-Mo-based electrocatalysts for hydrogen evolution under alkaline conditions

Min Luo,^a Jietian Yang,^a Xingang Li, D^a Miharu Eguchi,^{bc} Yusuke Yamauchi D^{bc} and Zhong-Li Wang **D^{**}***

Nickel-molybdenum (Ni-Mo) alloys are promising non-noble metal electrocatalysts for the hydrogen evolution reaction (HER) in alkaline water; however, the kinetic origins of their catalytic activities still remain under debate. In this perspective, we systematically summarize the structural characteristics of Ni-Mo-based electrocatalysts recently reported and find that highly active catalysts generally have alloy-oxide or alloy-hydroxide interface structures. Based on the two-step reaction mechanism under alkaline conditions, water dissociation to form adsorbed hydrogen and combination of adsorbed hydrogen into molecular hydrogen, we discuss in detail the relationship between the two types of interface structures obtained by different synthesis methods and their HER performance in Ni-Mo based catalysts. For the alloy-oxide interfaces, the Ni₄Mo/MoO₂ composites produced by electrodeposition or hydrothermal combined with thermal reduction exhibit activities close to that of platinum. For only the alloy or oxide, their activities are significantly lower than that of composite structures, indicating the synergistic catalytic effect of binary components. For the alloy-hydroxide interfaces, the activity of the Ni_xMo_y alloy with different Ni/Mo ratios is greatly improved by constructing heterostructures with hydroxides such as Ni(OH)2 or Co(OH)2. In particular, pure alloys obtained by metallurgy must be activated to produce a layer of mixed Ni(OH)₂ and MoO_x on the surface to achieve high activity. Therefore, the activity of Ni-Mo catalysts probably originates from the interfaces of alloy-oxide or alloy-hydroxide, in which the oxide or hydroxide promotes water dissociation and the alloy accelerates hydrogen combination. These new understandings will provide valuable guidance for the further exploration of advanced HER electrocatalysts.

Introduction

The increasing energy crisis induced by fast depletion of limited fossil fuels and environmental impacts have resulted in an urgent demand for clean and renewable energy resources. Owing to its high energy density and environmentally friendly characteristics, molecular hydrogen is an attractive energy carrier to meet future global energy demands.¹⁻⁴ Electrochemical water splitting that converts water into hydrogen and oxygen is a promising way for sustainable production of hydrogen, especially when it is driven by green electricity from sunlight, wind, hydropower, *etc.* Alkaline water electrolysis is one of the most mature and widely used electrolysis technologies for hydrogen

production due to its low-cost components and high durability. However, the sluggish reaction kinetics of the hydrogen evolution reaction (HER) in alkaline media lead to high overpotentials for practical water splitting. To promote the HER kinetics, efficient electrocatalysts are necessary to decrease the reaction overpotentials, thus making the water splitting more energy-saving. As a benchmark HER electrocatalyst, precious metal platinum (Pt)-based materials are almost still the catalysts with the highest intrinsic activity. Unfortunately, the scarcity and high cost of Pt seriously impede its large-scale applications in the electrocatalytic HER.

To develop efficient and earth-abundant alternatives to Pt as HER electrocatalysts, great efforts have been made to explore transition metal-based electrocatalysts over the past decade, including metal oxides, 6-8 metal alloys, 9-12 traditional metal phosphides, 13-17 carbides, 18,19 and sulfides. 20-22 Among them, nickel-based materials are the most used electrocatalysts in alkaline electrolyzers, and especially, nickel-molybdenum (Ni–Mo) bimetallic catalysts exhibit the best HER catalytic performance among all the non-noble metal-based materials. 23-42 Typically, Ni₄Mo alloy nanoparticles supported by MoO₂ cuboids on nickel foam exhibited zero onset overpotential, an

[&]quot;Tianjin Key Laboratory of Applied Catalysis Science and Technology, School of Chemical Engineering and Technology, Tianjin University, Tianjin 300072, China. E-mail: wang.zhongli@tju.edu.cn

^bJST-ERATO Yamauchi Materials Space-Tectonics Project and International Center for Materials Nanoarchitectonics (WPI-MANA), National Institute for Materials Science (NIMS), 1-1Namiki, Tsukuba, Ibaraki 305-0044, Japan

School of Chemical Engineering and Australian Institute for Bioengineering and Nanotechnology (AIBN), The University of Queensland, Brisbane, QLD 4072, Australia

overpotential of 15 mV at 10 mA cm⁻² and a low Tafel slope of 30 mV dec⁻¹ in 1 M KOH.²³ Such performance is comparable to that of Pt and superior to those of state-of-the-art Pt-free electrocatalysts. However, the detailed mechanism for the enhanced activity of Ni-Mo catalysts remains controversial, and several mechanisms have been proposed to account for the high HER activity of Ni-Mo-based electrocatalysts. One prevailing explanation is related to the electronic synergy of Ni and Mo in the alloy, leading to an appropriate hydrogen adsorption energy of the catalyst surface. 43,44 The second proposed mechanism is that Ni activates water dissociation to produce adsorbed hydrogen species which then transfer to the Mo surface via hydrogen spillover to produce molecular hydrogen, called the hydrogenspillover effect.45 And the third explanation is that the intrinsic activity of the Ni-Mo alloy originates from Ni and surface area enhancement through Mo dissolution improves the current density.46 These three mechanisms focus on the role of metallic Ni as the primary active site. However, the recent results demonstrated that a Mo oxo species (most likely Mo³⁺) supported on metallic Ni or the Ni_xMo_y alloy was responsible for the high activity of a Ni-Mo catalyst for water reduction to form hydrogen.47 It can be clearly seen that these mechanisms are inconsistent, indicating the complexity of the Ni-Mo catalytic system. Therefore, it is necessary to further explore the factors that affect the activity of the Ni-Mo catalyst and deeply understand the nature of high activity.

As shown in Fig. 1, the HER kinetics in alkaline solutions involves two steps: water dissociation to form adsorbed hydrogen (Volmer step) and combination of adsorbed hydrogen into molecular hydrogen (Heyrovsky or Tafel step). 48,49 Compared to the HER under acidic conditions, where protons are directly used as reactants, the reactants in an alkaline solution switch from protons to water as the hydrogen source, and an additional water dissociation step needs to occur to release protons, which

A Volmer:
$$H_2O + M + e^- \longrightarrow MH_{ads} + OH^-$$
 (1)

Heyrovsky:
$$H_2O + MH_{ads} + e^- \longrightarrow H_2 + M + OH^-$$
 (2)

Tafel:
$$MH_{ads} + MH_{ads} \longrightarrow H_2 + 2M$$
 (3)

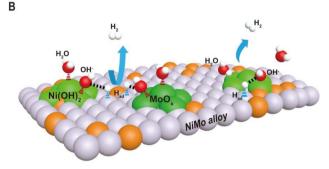



Fig. 1 (A) The reaction mechanism for the HER in alkaline electrolytes and two pathways are presented in the forms of the Volmer–Heyrovsky mechanism and the Volmer–Tafel mechanism. (B) Schematic diagram of synergetic catalysis of alloy–oxide or alloy–hydroxide interface structures, in which the oxide or hydroxide promotes water dissociation and the alloy accelerates hydrogen combination.

significantly decreases the reaction rate of the HER. As a result, even for Pt-based catalysts, the catalytic performance and kinetics are hindered by the slow rate of water cleavage in the Volmer step. Due to this reason, the reaction rate on Pt is usually 2-3 orders lower in an alkali than that in an acid. 50 Therefore, efficient HER under alkaline conditions requires that the active sites of the catalyst simultaneously accelerate the water dissociation and hydrogen combination reactions. Interestingly, the decoration of Ni(OH)2 on the Pt surfaces has been demonstrated to drastically increase the HER performance of Pt catalysts under alkaline conditions, and it is proposed that Ni(OH)2 promotes the cleavage of H-OH bonds in the water dissociation step, while Pt facilitates adsorption and combination of the generated hydrogen intermediates to form H2 molecules.5 Pt/Ni(OH)2based systems have not only advanced electrocatalytic performances but also provided insight into reaction mechanisms.

Inspired by the fundamental HER mechanism that occurs on Pt/Ni(OH)₂ interface, we systematically summarize the structural characteristics of Ni-Mo-based electrocatalysts recently reported, and find surprisingly that highly active catalysts generally have alloy-oxide or alloy-hydroxide interface structures. It is not difficult to speculate that the two components at the interface may jointly promote the two-step reaction of the HER in Ni-Mo systems. Based on this understanding, we discuss in detail the relationship between the two types of interface structures obtained by different synthesis methods and their HER performance in Ni-Mo-based catalysts. For the alloy-oxide interfaces, the Ni₄Mo/MoO_r (mixed oxide with the Mo ion valence from +4 to +6) composites produced by electrodeposition or hydrothermal combined with thermal reduction exhibit activities close to that of platinum. For only the alloy or oxide, their activities are significantly lower than that of composite structures, indicating the synergistic catalytic effect of binary components. For the alloyhydroxide interfaces, the activity of the Ni_xMo_y alloy with different Ni/Mo ratios is greatly improved by constructing heterostructures with hydroxides such as Ni(OH)2 or Co(OH)2. In particular, pure alloys obtained by metallurgy must be activated to produce a layer of mixed Ni(OH)2 and MoOx on the surface to achieve high activity. Therefore, it can be seen that the activity of Ni-Mo catalysts probably originates from the interfaces of alloy-oxide or alloy-hydroxide, in which the oxide or hydroxide promotes water dissociation and the alloy accelerates hydrogen combination. These new understandings will provide valuable guidance for the further exploration of advanced HER electrocatalysts.

Ni–Mo alloy/oxide interfaces

The preparation of the Ni-Mo alloy can be divided into two categories according to different raw materials: chemical method and metallurgical method. The chemical method generates alloys from Ni and Mo metal salts through a series of chemical reactions, while the metallurgical method directly produces alloys from two metals at high temperatures. Chemical methods are widely used in the synthesis of Ni-Mo alloy catalysts due to their advantages such as simple operation and controllable structure. According to the reaction process, chemical methods can also be divided into two types: one is the direct reduction of



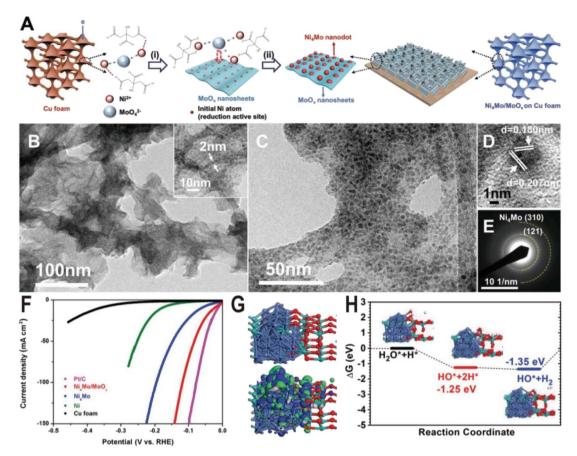


Fig. 2 (A) Schematic of the Ni₄Mo/MoO_x synthesis route on Cu foam. (i) Induced codeposition; (ii) formation of nanointerfaces with the dispersion of the alloy nanoparticles. (B and C) TEM images, (D) HRTEM image, and (E) SAED pattern of Ni_4 Mo nanoparticles on amorphous MoO_x nanosheets. (F) Polarization curves of Pt/C, bare Cu foam, Ni, Ni₄Mo alloy, and Ni₄Mo/MoO_x. (G) Electronic properties of interface model systems. Brown balls = Cu; cyan balls = Mo; blue balls = Ni; and red balls = O. (H) Free energy pathway, chemisorption, and formation energy for the HER. Reproduced with permission.⁵¹ Copyright 2019, Wiley-VCH.

metal salts to produce alloys in one step, such as electrochemical reduction deposition, and the other is the two-step method, i.e., the metal salts first form oxide intermediates, such as NiMoO₄ through a hydrothermal reaction, and then the intermediates are reduced in a hydrogen atmosphere to produce alloys. Since Mo⁶⁺ is more difficult to reduce than Ni²⁺, only part of Mo ions is reduced to form alloys during the reduction of metal salts or oxide intermediates, and excessive Mo ions will form oxides, resulting in a large number of alloy/oxide interface structures. Therefore, the proportion of Ni/Mo and the reduction conditions determine the composition of the products, mainly including the type of Ni-Mo alloy, the content, and valence of MoO_x. Under general chemical reduction conditions, such as electrochemical reduction or hydrogen reduction below 600 °C, the Ni-Mo alloy is mainly Ni₄Mo, and MoO_x is a mixed oxide with the Mo ion valence from +4 to +6. In the following, we will introduce several Ni-Mo-based catalysts prepared by a chemical method, focusing on the interface structures of N₄Mo/MoO_x and their HER performances.

The Ni₄Mo nanodot/amorphous MoO_x nanosheet interface structure was synthesized on copper foam via a one-step electrodeposition process as shown in Fig. 2A.51 In the electrodeposition process, the $\mathrm{MoO_4}^{2-}$ anions, Ni^{2^+} cations, and the citrate

anions first formed [(NiCit)(MoO_x)]_{ads}⁻, followed by the reduction of Ni²⁺ to metallic Ni⁰, and then the resulting Ni atoms acted as the active sites for the depositing the Ni₄Mo alloy on the MoO_r surface. By changing the ratio of Ni/Mo and electroreduction current density, the samples of Ni₄Mo and pure Ni were also synthesized for the comparison experiment. The as-synthesized composite catalyst exhibits ultrathin nanosheet morphology (Fig. 2B) and many nanoparticles with a diameter of about 5 nm are homogeneously distributed on the nanosheets (Fig. 2C). The high-resolution transmission electron microscope (HRTEM) image (Fig. 2D) and selective area electron diffraction (SAED) pattern (Fig. 2E) show lattice fringes of (121) and (310) planes of the Ni₄Mo nanoparticle, while no crystal lattice of MoO_x nanosheets could be observed, suggesting the amorphous nature of the MoO_x nanosheets. The strong Raman peaks in the range of 550-1000 cm⁻¹ also verify the presence of amorphous molybdenum oxide, and the X-ray photoelectron spectroscopy (XPS) with Ar etching shows that all Ni²⁺ is reduced to Ni⁰, while the Mo element exists not only in the form of Mo⁰ but also oxidized forms including Mo⁴⁺ and Mo⁵⁺. Fig. 2F shows the polarization curves of Ni metal, Ni₄Mo alloy, and Ni₄Mo/MoO_x for HER electrocatalysis. The overpotential of Ni₄Mo/MoO_x at a current density of 10 mA cm⁻² is only 16 mV, close to that of Pt/C, and

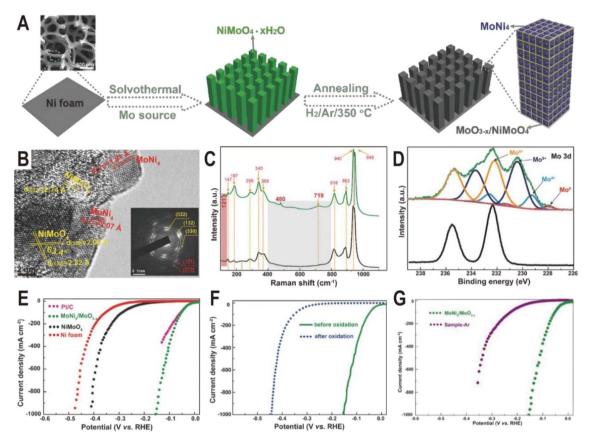


Fig. 3 (A) Schematic illustration of the formation of $MoNi_4/MoO_{3-x}$ nanorod arrays on Ni foam. (B) HRTEM image for $MoNi_4/MoO_{3-x}$ (inset: SAED pattern). (C) Raman spectra of NiMoO₄ (black) and MoNi₄/MoO_{3-x} (green). (D) Mo 3d XPS spectra of NiMoO₄ (black) and MoNi₄/MoO_{3-x} (green). (E) Polarization curves for Pt/C, Ni foam, NiMoO₄, and MoNi₄/MoO_{3-x}. (F) Polarization curves of MoNi₄/MoO_{3-x} for the HER before and after electrochemical oxidation. (G) Polarization curves of MoNi₄/MoO_{3-x} and NiMoO₄ annealed in an Ar atmosphere (sample-Ar). Scan rate: 2 mV s⁻¹ Reproduced with permission.⁵² Copyright 2017, Wiley-VCH.

much lower than that of Ni metal (169 mV) and the Ni₄Mo alloy (40 mV). Evidently, the HER activity of Ni increases substantially by forming an alloy with Mo and is further boosted by constructing the Ni₄Mo/MoO_x nanointerfaces, indicating the beneficial bimetallic ligand effect and synergetic effect between the metal and metal oxide. The theoretical study shows that the Ni₄Mo/MoO_x has a strong bonding at the interface and the electronic distribution indicates that the Ni₄Mo alloy is more electron-rich (Fig. 2G), compared with the hole-rich MoO_x. The comparison of projected density of states (PDOS) indicates that the d-band center of Ni at the interface downshifts toward lower energy levels, which optimizes the bonding strength of *H on the alloy. In MoO_x, the deep localized O-2p band overlaps with the Mo-4d-t2g state propelling more electrons towards the Mo-4d-eg level, which leads Mo sites to high binding activities for the Orelated species such as *OH intermediates. Therefore, Ni₄Mo/ MoO_x interface provides a high active area for bond-cleavage of water-splitting under alkaline conditions. The free energy profile for the HER pathway under alkaline conditions is also studied (Fig. 2H), and the Ni₄Mo/MoO_x interface shows substantial energetic favorable with reaction energy (-1.35 eV) gained for the

In addition to one-step direct reduction, the two-step method is also widely used in the synthesis of the Ni₄Mo/MoO_x interface.

Typically, NiMoO₄ nanorod arrays were first grown on Ni foam via a solvothermal process using Ni foam itself as a Ni source and ammonium molybdate as a Mo source, and then NiMoO4 was partially decomposed to MoNi₄ nanocrystals and amorphous MoO_{3-x} by annealing in a H₂/Ar atmosphere at 350 °C (Fig. 3A).⁵² The HRTEM image (Fig. 3B) displays clear lattice fringes with distances of 1.81 and 2.07 \ corresponding to the (310) and (121) planes of the MoNi₄ alloy, suggesting the production of MoNi₄ nanocrystals. Due to the amorphous phase of MoO_{3-x} , no continuous lattice fringes are observed in the HRTEM image, but Raman and XPS spectra clearly evidence the existence of MoO_{3-r} . As shown in Fig. 3C, the annealed $MoNi_4/MoO_{3-x}$ exhibits three new peaks at 121, 480, and 719 cm⁻¹ compared to the NiMoO₄ precursor, and the three peaks could be ascribed to the lattice deformation mode, deformation of Mo=O stretching mode, and modification of the Mo₂-O bond for MoO_{3-x} species, respectively. The high-resolution Mo 3d XPS spectra (Fig. 3D) of MoNi₄/ MoO_{3-x} further demonstrate the existence of Mo^0 , Mo^{4+} , Mo^{5+} and Mo⁶⁺, and the low-valence states of Mo (Mo⁵⁺ and Mo⁴⁺) imply the formation of MoO_{3-x} with oxygen vacancies. As dual active components, the MoNi₄/MoO_{3-x} hybrid exhibits a remarkable HER activity with low overpotentials of 17 mV at 10 mA cm⁻² and 114 mV at 500 mA cm⁻² (Fig. 3E), comparable to the values of the Pt catalyst (13 and 59 mV). The turnover

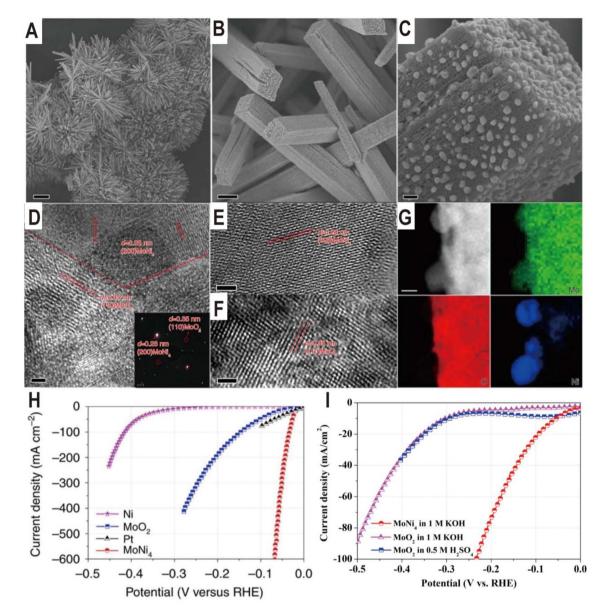


Fig. 4 (A-C) Typical SEM images of MoNi₄/MoO₂@Ni. Scale bars, (A) 20 μ m; (B) 1 μ m; (C) 100 nm. (D-F) HRTEM images of MoNi₄/MoO₂@Ni. The inset image in (D) is the related selected-area electron diffraction pattern of the MoNi₄ electrocatalyst and the MoO₂ cuboids. Scale bars, (D-F) 2 nm; inset in (D), 11/nm. (G) Corresponding elemental mapping images of the MoNi₄ electrocatalyst and the MoO₂ cuboids. Scale bars: 20 nm. (H) Polarization curves of the MoNi₄ electrocatalyst supported by the MoO₂ cuboids, pure Ni nanosheets, and MoO₂ cuboids on nickel foam. (I) Polarization curves of the MoO₂ nanosheets and the MoNi₄ electrocatalyst supported by the MoO₂ cuboids on carbon cloth in different electrolytes. Reproduced with permission.²³ Copyright 2017, Springer Nature.

frequency (TOF) is also estimated, and at an overpotential of 100 mV, the TOF of $MoNi_4/MoO_{3-x}$ is $1.13 \, s^{-1}$, much higher than that of Ni foam $(0.06 \, s^{-1})$. After the 20 h chronoamperometry test at 20 or 30 mA cm⁻², the decline of overpotential is negligible and the structure of nanorod arrays and composition remain almost unchanged, keeping the similar valence states of Mo^0 , Mo^{4+} , and Mo^{5+} . In order to investigate the origin of intrinsic activity, the Mo^0 and Ni^0 as well as Mo^{4+} and Mo^{5+} in $MoNi_4/MoO_{3-x}$ were oxidized to the high valence states of Mo^{6+} and Ni^{2+} by *in situ* electrochemical oxidation. As a result, HER activity decreases significantly (Fig. 3F), indicating that the activity of high valence molybdenum oxide is very low. Interestingly, the

control sample annealed in an Ar atmosphere exhibits better activity than the completely oxidized sample due to the existence of little MoO_{3-x} ; however, since there is no $MoNi_4$ alloy produced, its activity is still much lower than that of the samples obtained in a reducing atmosphere (Fig. 3G). Therefore, the $MoNi_4$ alloy and MoO_{3-x} should synergistically catalyze the HER at the interface. Other $MoNi_4/MoO_{3-x}$ or $MoNi_4/NiMoO_x$ interfaces with different structures such as hollow, branch-leaf hierarchical, or nanowire structures have been prepared by reducing the $NiMoO_4$ intermediate, and all exhibited excellent HER performance with the overpotentials from 29 to 38 mV at 10 mA

cm⁻², further demonstrating the unique advantages of Ni₄Mo/ MoO_r interfaces. 53-56

The Ni₄Mo/MoO_x interface structure of different components can be derived from the NiMoO₄ intermediate by regulating the reduction temperature. The reduction temperature determines the reduction degree of Mo⁶⁺ ions in MoO_r. For example, the Ni₄Mo/MoO₂ interface was obtained by reducing NiMoO₄ cuboids in a H₂/Ar atmosphere at 500 °C for 2 h.²³ The NiMoO₄ cuboids were grown beforehand on a piece of nickel foam via a hydrothermal reaction, and after reduction, MoNi₄ nanoparticles were directly constructed on the surfaces of the MoO₂ cuboids (Fig. 4A-C). The HRTEM images of the samples show lattice fringes with lattice distances of 0.35 and 0.28 nm, which correspond to the (110) facet of MoO2 and the (200) facet of MoNi₄, respectively (Fig. 4D-F). The energy-dispersive X-ray spectroscopy (EDX) analysis indicates that the surface nanoparticles are constituted by only Mo and Ni with an atomic ratio of 1:3.84 (Fig. 4G), which well approaches 1:4. The polarization curves (Fig. 4H) show a zero onset potential and the overpotentials at current densities of 10 and 200 mA cm⁻² for the Ni₄Mo/MoO₂ electrocatalyst were as low as 15 and 44 mV, respectively, which are significantly lower than the values for the

Ni nanosheets, MoO₂ cuboids, and commercial Pt/C. For the Pt/C electrocatalyst, it exhibits an overpotential of only 10 mV at a current density of 10 mV cm⁻², but the maximum current density only reaches 80 mA cm⁻² due to the Pt catalyst significantly peeling off from the support. In contrast, the threedimensional (3D) cuboid array grown in situ on Ni foam enables the current density of Ni₄Mo/MoO₂ to reach 600 mA cm⁻². Therefore, in addition to intrinsic activity, the 3D structure of the catalyst is also critical to the activity. Based on the electrochemical double-layer capacitances, the TOF of MoNi₄/MoO₂ is calculated to be 0.4 s⁻¹ at the overpotential of 50 mV, which is higher than the TOF values of the previously reported Pt-free electrocatalysts. In addition, it can be seen from the polarization curve that MoO2 cuboids have a certain HER activity, which is much higher than that of Ni nanosheets. Interestingly, the HER activity of MoO₂ loaded on carbon paper in acidic and alkaline media is very close (Fig. 4I), which indicates that the additional water dissociation in alkaline media does not reduce the reaction rate, and the overall low activity indicates that the binding capacity of H on MoO₂ surface is poor. The Ni₄Mo alloy just makes up for this shortcoming, and the combination of the two produces complementary and synergistic effects. The highly

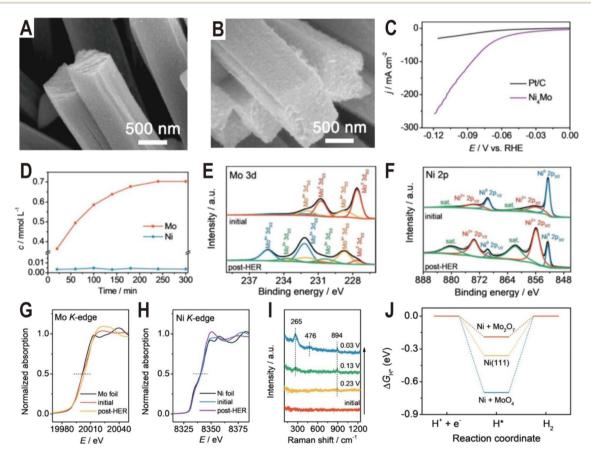


Fig. 5 SEM images of the (A) as-prepared Ni₄Mo nanorod arrays and (B) Ni₄Mo nanorod arrays after the HER test for 12 h. (C) Polarization curves of the Ni₄Mo alloy and Pt/C. (D) Time-dependent concentration of dissolved Mo and Ni in the electrolyte of the Ni₄Mo alloy. (E) Mo 3d and (F) Ni 2p XPS spectra of Ni₄Mo before and after the HER test. (G) Mo K-edge and (H) Ni K-edge XANES spectra of Ni₄Mo before and after the HER test. (I) Potential-dependent in situ Raman spectra of Ni₄Mo during the alkaline HER process. (J) Free energy diagrams of the HER on bare Ni(111), Ni(111) + MoO₄, and Ni(111) + Mo₂O₇. Reproduced with permission.⁵⁸ Copyright 2021, Wiley-VCH.

active Ni₄Mo/MoO₂ interface has also been demonstrated on

other substrates such as stainless-steel wires obtained from worn-out tires (the overpotentials at the current densities of 100 and 200 mA cm⁻² were only 63 and 77 mV, respectively).⁵⁷

Chemical Science

The Ni₄Mo/MoO_x active interface can be generated not only by controlling the synthesis conditions but also in the electrochemical activation process. Typically, it is demonstrated that some Mo in Ni₄Mo is oxidized during the activation process and dissolved in the form of MoO₄²⁻.58 Then, the dissolved MoO₄²⁻ will re-adsorb on the alloy surface and polymerize into the dimer $Mo_2O_7^{2-}$ to form a highly active Ni_4Mo (or Ni)/ $Mo_2O_7^{2-}$ interface. Fig. 5A and B show the SEM images of the as-prepared Ni₄Mo nanorod arrays before and after the HER test. After the electrochemical activation, the nanorod array structure is nearly unchanged, except for the roughened surface and increased porosity. As shown in the polarization curves of Fig. 5C, the activated Ni₄Mo displays an extremely low overpotential of only 86 mV at 100 mA cm⁻², which is much better than that of commercial 20% Pt/C with the same mass loading. By analyzing the content of Mo and Ni in the electrolyte, it is found that the content of Ni keeps at a low level throughout the activation process while the content of Mo increases with time and reaches the summit after 4 h (Fig. 5D). The Mo 3d XPS spectra (Fig. 5E) show that the peaks of Mo⁰ obviously decrease after the HER test, while the peaks of Mo⁴⁺, Mo⁵⁺, and Mo⁶⁺ notably increase, indicating the oxidation of Mo. Similarly, in the Ni 2p XPS spectra (Fig. 5F), the ratio of Ni²⁺ also increases. X-ray absorption near edge structure (XANES) is further employed to investigate the change of valence state of Mo and Ni. In the Mo K-edge spectra (Fig. 5G), the post-HER absorption edge is obviously larger than that of the initial one, confirming the oxidation of Mo, while for the Ni K-edge spectra (Fig. 5H), both the initial and the post-HER samples show a similar absorption edge to Ni foil, indicating that Ni is mainly zero valent in the reaction process. In situ Raman spectra are then used to explore the change of Mo species during HER activation (Fig. 5I). Initially, there is no Raman signal, and after applying a voltage of 0.23 V, a peak centered at 894 cm⁻¹ first appears, which can be assigned to Mo=O symmetric stretching vibration in the MoO₄ tetrahedron, indicating the production of MoO₄²⁻ ions. Interestingly, with the potential decreasing, another two peaks at 265 and 476 cm⁻¹ arise and become strong, both of which correspond to the deformation mode and symmetric stretching mode of Mo-O-Mo, respectively. The appearance of these two new peaks indicates the possible polymerization of MoO₄²⁻ into the dimer of $Mo_2O_7^{2-}$. The DFT calculations further demonstrate that the Ni (Ni₄Mo)/Mo₂O₇²⁻ interface optimizes the bonding energy with the adsorbed hydrogen (Fig. 5J).

Ni_xMo_v alloy/hydroxide interfaces 3.

Except oxides, metal hydroxides such as Ni(OH)2 and Co(OH)2 are another kind of active component to promote the dissociation of water for the HER. For example, the Ni(OH)2 modified Mo_{0.84}Ni_{0.16} alloy exhibited significantly enhanced activity for the HER compared to the unmodified alloy.⁵⁹ The synthesis process of Mo_{0.84}Ni_{0.16}@Ni(OH)₂ hybrids is illustrated in Fig. 6A. First the NiMoO₄ nanowire precursors were grown on Ni foam by a facile hydrothermal process and then were calcined in a H₂/Ar atmosphere to obtain the NiMoO₄-Mo_{0.84}Ni_{0.16} composites. Subsequently, the Ni(OH)2 nanosheets were modified on the surface of the composites by electrodeposition. As a result, the Mo_{0.84}Ni_{0.16} alloy and Ni(OH)2 nanosheets formed a heterostructure $(Mo_{0.84}Ni_{0.16}@Ni(OH)_2)$. The HRTEM image of the interface (Fig. 6B) demonstrates the lattice distance of 0.27, 0.23, 0.20, and 0.34 nm, which corresponds to the (100), (101), (240), and (040) planes of Ni(OH)2, respectively, and the crystalline lattice distance of 0.24 nm and 0.28 nm corresponds to the (111) plane of $Mo_{0.84}Ni_{0.16}$ and (-111) plane of $NiMoO_4$, respectively. In the O 1s XPS spectra (Fig. 6C), the intensity of the OH⁻ peak becomes strong in Mo_{0.84}Ni_{0.16}@Ni(OH)₂ compared to NiMoO₄-Mo_{0.84}Ni_{0.16} and both O 1s peaks also exhibit a positive shift, suggesting the strong electronic interaction between Mo_{0.84}Ni_{0.16} and Ni(OH)2. As expected, due to the abundant interface structure and synergistic effect between Mo_{0.84}Ni_{0.16} and Ni(OH)₂, the Mo_{0.84}Ni_{0.16}(a)Ni(OH)₂ heterostructure exhibited high HER activity with a very small overpotential at 10 mA cm⁻² (10 mV), low Tafel slope (71 mV dec⁻¹), and excellent stability (100 h) (Fig. 6D-F), which is much better than that of unmodified NiMoO₄-Mo_{0.84}Ni_{0.16}. After the 100 h stability test, the SEM image of Mo_{0.84}Ni_{0.16}@Ni(OH)₂ (the inset of Fig. 6F) displays the consistent surface morphology with the original Mo_{0.84}Ni_{0.16}@-Ni(OH)₂ Another more complex heterostructure is composed of Ni₄Mo, Ni₃N, Ni, and Ni(OH)₂ (Fig. 6G and H), which was synthesized by low-temperature H₂/N₂ plasma activation of Modoped Ni(OH)2 nanosheets arrays (P-Mo-Ni(OH)2 NSAs).60 Due to the synergistic effect of different components, especially the interaction between Ni₄Mo and Ni(OH)₂, the optimized heterostructure only needs a low overpotential of 22 and 98 mV to deliver a current density of 10 and 100 mA cm⁻² (Fig. 6I), respectively. At an overpotential of 50 mV, the TOF value of P- $Mo-Ni(OH)_2$ is 1.325 s⁻¹, which is much larger than that of Ni $(OH)_2$ (0.42 s⁻¹). After the 100 h stability test at an overpotential of 22 mV, the HRTEM image, XRD pattern, and XPS spectra imply that metallic Ni, Ni₄Mo alloy, Ni₃N, and Mo incorporated Ni(OH)2 still exist. Moreover, it is found that the Mo concentration in the electrolyte first increases from 0 to 1.13 ppm and then remains relatively stable, and except for the dissolution of a certain amount of Mo and N and the oxidation of some amount of metallic Ni, the chemical composition and valence states of the P-Mo-Ni(OH)2 change little during the HER. Theoretical and experimental studies show that the metallic Ni₄Mo optimizes the Gibbs free energy for hydrogen adsorption and Ni(OH)2 can weaken the HO-H bond of absorbed water to facilitate water dissociation in the hetero-interface of Ni₄Mo/Ni(OH)₂.

Ni(OH)2 on the NiMo alloy surface can not only be modified additionally but also be produced in situ by introducing Fe ions. It has been demonstrated that the presence of Fe on the surface of the Ni₄Mo alloy can induce the conversion of the Ni to Ni(OH)₂ by forming the Fe-(OH)₄-Ni₄ motif.⁵⁰ This catalyst is composed of hydroxide-mediated Ni₄Mo nanoparticles decorated with FeO_r and anchored onto MoO₂ nanosheets (h-NiMoFe). It was prepared by a two-step method: Fe-doped NiMoO₄ microsphere precursors (Fe-NiMoO₄) were first grown

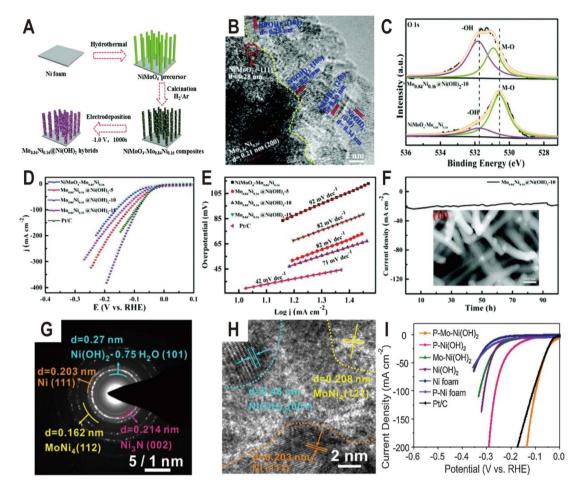


Fig. 6 (A) Schematic illustration of the preparation of the $Mo_{0.84}Ni_{0.16}@Ni(OH)_2$ heterostructure. (B) HRTEM image of $Mo_{0.84}Ni_{0.16}@Ni(OH)_2$. (C) The high-resolution XPS spectra of O 1s for $NiMoO_4-Mo_{0.84}Ni_{0.16}$ composites and the $Mo_{0.84}Ni_{0.16}@Ni(OH)_2$ heterostructure. (D and E) Polarization curves and the corresponding Tafel plots of NiMoO $_4$ -Mo $_{0.84}$ Ni $_{0.16}$, and Mo $_{0.84}$ Ni $_{0.16}$ @Ni(OH) $_2$ with different deposition times of 5, 10, and 15 min, and Pt/C. (F) The chronoamperometric curve at an overpotential of 34 mV for Mo_{0.84}Ni_{0.16}@Ni(OH)₂. The inset is the SEM image after the stability test. Reproduced with permission. 59 Copyright 2020, Royal Society of Chemistry. (G and H) SAED pattern and HRTEM image of P-Mo-Ni(OH)₂ NSAs. (I) Polarization curves of Ni foam, P-Ni foam, Ni(OH)₂ NSAs, Mo-Ni(OH)₂ NSAs, P-Ni(OH)₂ NSAs, P-Mo-Ni(OH)₂ NSAs, P-Ni(OH)₂ NSAS, Pand Pt/C. Reproduced with permission.⁶⁰ Copyright 2020, Elsevier.

on Ni foam by the hydrothermal method and then reduced at 500 °C in a Ar/H₂ atmosphere. The TEM image (Fig. 7A) shows that the catalyst is composed of ultrathin nanosheets with nanoparticles anchored onto them and the HRTEM images (Fig. 7B and C) show typical lattice spacings of 0.24 nm and 0.20 nm, corresponding to the (020) plane of MoO₂ and the (220) plane of Ni₄Mo, respectively, and no Fe-based compounds are detected. The polarization curves in Fig. 7D show that the activity of h-NiMoFe is much better than that of NiMo and Ni samples, indicating that alloying of Ni₄Mo and addition of Fe play vital roles in the good performance of the h-NiMoFe catalyst. The overpotential of h-NiMoFe at 10 mA cm⁻² is only 14 mV and even at an increased current density of 1000 mA cm⁻², the overpotential is still very low (98 mV). After 40 h continuous operation, h-NiMoFe shows good stability and maintains its crystalline structure well. In the Ni 3s XPS spectra, it is found that there is a higher content of surface hydroxide on h-NiMoFe than those on the control NiMo and Ni samples due to the introduction of Fe (Fig. 7E). In situ XAS characterization results

indicate that a new chemical species containing the Fe-O(H)-Ni motif forms and FT-EXAFS fitting results show that an iron site is coordinated by four O atoms (or OH groups) and four Ni atoms. Density functional theory (DFT) calculations confirm the local structure of one Fe connecting to four hydroxylated Ni sites on the Ni₄Mo surface (denoted as Fe-(OH)₄-Ni₄, Fig. 7F and G). The added iron in h-NiMoFe extracts electrons from Ni atoms to lead to more unoccupied states of Ni sites, which remarkably changes the charge distribution of Ni sites. The comparison of PDOS shows that the d-band centers of Ni in h-NiMoFe exhibit more negative energy than the NiMo catalyst, indicating a stronger H bonding behavior. The energy diagrams of Gibbs free energies further show nearly 0 eV adsorption free energy of H ($\Delta G_{\rm H}$) and a much lower energy barrier and fast kinetics for water dissociation for h-NiMoFe compared to Pt (Fig. 7H and I). In addition to Ni(OH)2, this system also contains MoO2, which can also promote water dissociation as discussed above, so this system may be a catalytic system with synergistic effects of two interfaces: Ni₄Mo/Ni(OH)₂ and Ni₄Mo/MoO₂.

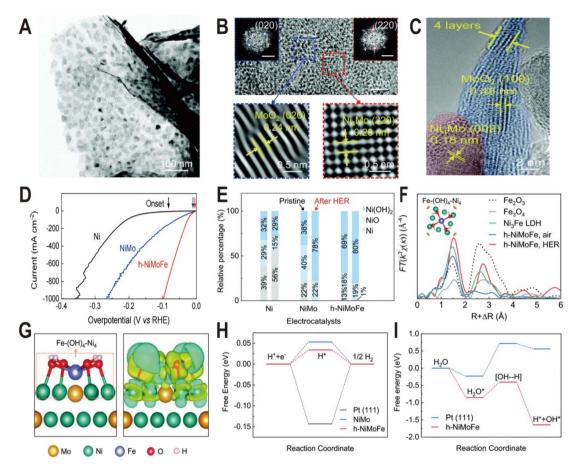


Fig. 7 (A) TEM image of the h-NiMoFe catalyst. (B and C) HRTEM images of h-NiMoFe. (B) An enlarged view of h-NiMoFe, lattice fringes of a MoO₂ nanosheet (blue box) and Ni₄Mo nanoparticles (red box), scale bars in the insets are 5 1/nm; (C) side view of the MoO₂ nanosheet. (D) Polarization curves of h-NiMoFe and its control samples. (E) Relative percentages of surface Ni species from the Ni 3s XPS spectra on the Ni, NiMo, and h-NiMoFe samples before and after the HER test. (F) FT-EXAFS of the h-NiMoFe catalyst and control samples at Fe K-edges. (G) Calculated relaxed configuration of an Fe-(OH)₄-Ni₄ motif on a Ni₄Mo (002) slab and the corresponding charge density difference in this configuration. (H and I) Adsorption energies for H and dissociated H₂O on h-NiMoFe and control samples. Reproduced with permission. Copyright 2021, Royal Society of Chemistry.

Similar to Ni(OH)₂, Co(OH)₂ is also used to modify the NiMo alloy to improve the HER performance. The Co(OH)2 cavity arrayencapsulated NiMo alloy on carbon cloth (Co(OH)2/NiMo CA@CC) was prepared by a two-step electrodeposition route. 61 As shown in Fig. 8A, the NiMo alloy was first deposited on carbon cloth by chronopotentiometry (defined as NiMo@CC). And then, with the assistance of a layer of polystyrene (PS) template, Co(OH)2 was confined to nucleate and grow around the PS microspheres by the second electrodeposition. After dissolving the PS template, the uniform and ordered Co(OH)₂ cavity array was obtained on the surface of NiMo@CC (defined as Co(OH)2/ NiMo CA@CC). The NiMo alloy is composed of uniform nanoparticles with an average size of \sim 70 nm and these nanoparticles are connected to the Co(OH)2 thin nanosheets. The HRTEM image at the boundary shows lattice fringes with a distance of 0.21 and 0.25 nm (Fig. 8B), corresponding to the (111) plane of Ni metal and the (100) plane of α -Co(OH)₂, respectively, suggesting that metallic Ni as the dominant phase exists in the Ni_xMo_y alloy and forms a heterojunction interface with Co(OH)2. From the

XPS spectra (Fig. 8C-E), it is found that both the Ni 2p peaks and Mo 3d peaks in Co(OH)2/NiMo CA@CC are shifted by 0.4 and 0.5 eV toward the lower binding energy relative to those of NiMo@CC, respectively, while the characteristic peaks of Co 2p are shifted toward high binding energy by 0.8 eV (Fig. 8E), indicating the transfer of electrons from Co of Co(OH)2 to the surface of the NiMo alloy. The HER polarization curves (Fig. 8F) show that Co(OH)₂/NiMo CA@CC exhibits the highest catalytic activity among NiMo@CC, Co(OH)2@CC, and NiMo/ Co(OH)2@CC with an overpotential of 30 mV to reach 10 mA cm⁻². The comparative experiments demonstrate that the coupling of NiMo with Co(OH)2 and the cavity array structure can effectively boost the HER activity. The Gibbs free energy diagram (Fig. 8G) shows that water is more easily adsorbed on Co(OH)₂ than on NiMo alloy, and the energy barrier to break the H-OH bond is only 0.58 eV on Co(OH)2, which is much lower than that of the NiMo alloy (up to 1.04 eV), indicating that the introduction of Co(OH)2 substantially accelerates the kinetics of the water adsorption and dissociation steps. Moreover, from the PDOS of

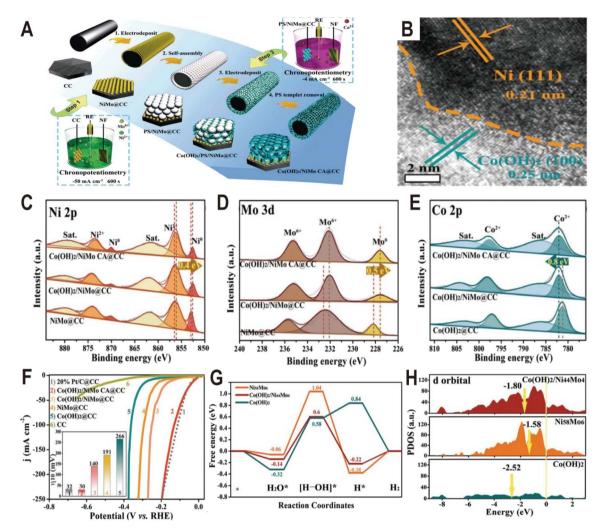


Fig. 8 (A) Synthetic illustration of the fabrication process of Co(OH)₂/NiMo CA@CC. (B) HRTEM image of NiMo alloy particles from Co(OH)₂/ NiMo CA@CC. (C-E) XPS spectra of Ni 2p, Mo 3d, and Co 2p of Co(OH)₂/NiMo CA@CC, Co(OH)₂/NiMo@CC, NiMo@CC, and Co(OH)₂@CC. (F) Polarization curves of bare CC, Co(OH)₂/NiMo CA@CC, Co(OH)₂/NiMo@CC, NiMo@CC, Co(OH)₂@CC, and Pt/C@CC toward the HER in 1.0 M KOH. (G) The free energy diagram for the HER on the surface of $Ni_{58}Mo_6$ and $Co(OH)_2$, and the interface of $Co(OH)_2/Ni_{44}Mo_4$. (H) The projected density-of-states of d orbitals of Ni₅₈Mo₆, Co(OH)₂, and Co(OH)₂/Ni₄₄Mo₄ with aligned Fermi levels. Reproduced with permission.⁶¹ Copyright 2021, Wiley-VCH.

d orbitals (Fig. 8H), the d-band center of Co(OH)₂/NiMo (-1.80 eV) is downshifted relative to the single NiMo (-1.58 eV), which can weaken the bonding strength of H and thus promote the H2 evolution.

In addition to the interfaces of controllable synthesis, the Ni_xMo_y alloy/hydroxide interface can also be generated during electrochemical activation. For the NixMov alloys obtained by high-temperature metallurgy, their HER activities are generally not high due to the lack of an interface structure, but their activities will be greatly improved after electrochemical activation to produce a layer of $Ni(OH)_2$ or MoO_x on the surface. A typical example is the nanosponge-like Ni_{0.33}Mo_{0.67} solid solution catalyst synthesized via a one-step high-temperature (900 °C) sintering method by using metallic Ni, Mo, and magnesium (Mg) powders (Fig. 9A).62 Spherical Mg powder was added as a poremaking agent to prepare nanoporous alloys. The HRTEM image of the Ni_{0.33}Mo_{0.67}-900 solid solution shows an interplanar

spacing of 0.221 nm (Fig. 9B), corresponding to the (110) facet of the metallic Mo body-centered cubic (bcc) structure. Interestingly, after an activation of 200 cycles with a scan rate of 10 mV s⁻¹ and an overpotential range of 0-0.447 V (vs. RHE), an (oxy)hydroxide layer with a thickness of approximately 8 nm was clearly formed on the surface of $Ni_{0.33}Mo_{0.67}$ -900, as shown in Fig. 9C. XPS spectra further prove the change of surface composition before and after activation. For Ni 2p (Fig. 9D), after aging, the peaks of Ni^o and Ni³⁺ at 852.4 eV and 855.8 eV disappear and the peak of Ni²⁺ at 855.6 eV is produced, corresponding to a phase of Ni(OH)₂. For Mo 3d (Fig. 9E), the relative amount of Mo⁰, Mo⁴⁺, and Mo⁵⁺ species in the activated sample rapidly decreases relative to the pristine sample; in contrast, Mo6+ increases, indicating the formation of high valence MoO_r. For O 1s (Fig. 9F), the peak intensity of hydroxyl groups has an obvious increase. The polarization curves in Fig. 9G show that the activated Ni_{0.33}Mo_{0.67}-900 solid solution catalyst exhibits a lower overpotential of 37 mV at

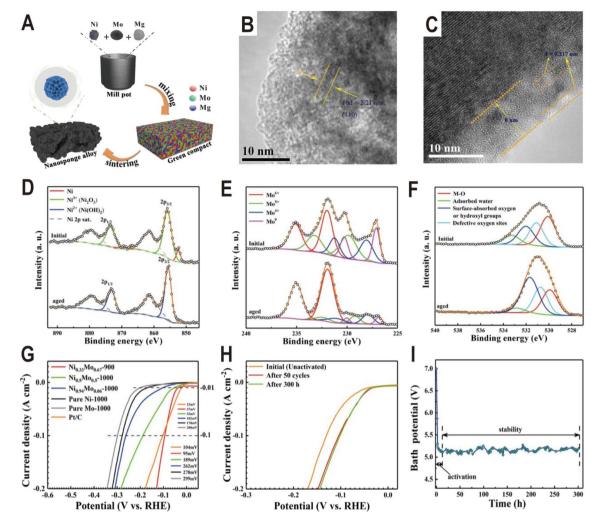


Fig. 9 (A) Schematic diagram of the fabrication process for a nanosponge-like NiMo solid solution prepared by high-temperature sintering. (B and C) HRTEM images of Ni_{0.33}Mo_{0.67}-900 before and after the HER test. (D-F) Ni 2p, Mo 3d, and O 1s XPS spectra of Ni_{0.33}Mo_{0.67}-900 before and after aging. (G) Polarization curves of pure Ni-1000, pure Mo-1000, Ni_{0.94}Mo_{0.06}-1000, Ni_{0.5}Mo_{0.5}-1000, Ni_{0.33}Mo_{0.67}-900, and Pt/C $electrodes\ in\ a\ 1\ M\ KOH\ solution.\ (H)\ Comparison\ of\ polarization\ curves\ of\ Ni_{0.33}Mo_{0.67}-900\ obtained\ under\ different\ conditions.\ (I)\ Bath\ voltage$ variations at a current density of 2 A cm⁻² in 1 M KOH solution. Reproduced with permission.⁶² Copyright 2020, American Chemical Society.

a current density of 10 mA cm⁻², and the performance of the sample without activation is obviously lower than that of the sample (Fig. 9H). The stability test curve also shows an obvious activation process, and the bath voltage demonstrates a fast decrease in the initial period of electrolysis, as shown in Fig. 9I. After activation, the Ni_{0.33}Mo_{0.67}-900 solid solution possesses an ultrahigh stability (>300 h) at 2 A cm⁻² in a 1 M KOH electrolyte. As another example, the plasma sprayed RANEY®-type NiMo electrode also forms a layer of Ni(OH)2 and MoO2 after chemical activation.63 Due to proper micropore/macropore distribution, appropriate amounts of active nickel and molybdenum species, and the oxidation degree, the activated NiMo electrode delivered a high current density of 200 mA cm⁻² at 82 mV and stabilized with no measurable degradation over 47 days for the HER in 30 wt% KOH.

From the above example analysis, it can be seen that the Ni_x-Mo_v alloy/hydroxide interface exhibits a bi-functional effect to simultaneously promote the dissociation of water and the

combination of adsorbed hydrogen. The kinetics of the HER in alkaline solutions will depend both on the rate of desorption of OHad to accommodate the adsorption of H2O on hydroxide and on the rate of Had recombination, which is optimized on the alloy. For the dissociation of water, the activity will be controlled by the bond strength between metal hydroxides M(OH)_x and OH_{ad}. In order to explore their interaction, a descriptor, OH-M^{2+ δ} bond strength ($0 \le \delta \le 1.5$), was proposed, and it was found that the activity trend was Mn < Fe < Co < Ni, which was inversely proportional to the OH- $M^{2+\delta}$ strength of Ni < Co < Fe < Mn.⁶⁴ For the Fe and Mn hydroxides, due to their strong bonding with OH_{ad} , OH_{ad} cannot be desorbed and the reaction cannot continue, resulting in 'poisoning' of the surface. In contrast, for Ni hydroxides that bind OHad neither too strongly nor too weakly, the maximum activity was realized for the HER. Thus, the overall rate of the HER may, in principle, be controlled by optimizing the density and the nature of the sites required for dissociation of water on M(OH)_x, as well as the OH–M^{2+ δ} and alloy-H_{ad} energetics.

Table 1 Electrochemical performances of highly active Ni-Mo-based catalysts with alloy-oxide interfaces in 1 M KOH

Electrocatalyst	Synthesis method	Composition and structure	Onset potential (mV)	Overpotential (mV)	$TOF(s^{-1})$	Tafel slope (mV per decade)	Stability	Ref.
${ m Ni_4Mo/MoO_x/Cu}$	Electrodeposition	Ni ₄ Mo, MoO _x , nanosheets	0	$\eta_{10} = 16, \eta_{250} = 105 (70 $ °C, 30% KOH)	- - 0.	64	10 mA cm ⁻² , 24 h, 50 mA cm ⁻² , 24 h, 100 mA cm ⁻² , 24 h, 100 mA cm ⁻² , 24 h	51
$MoNi_4/MoO_{3-x}$	Hydrothermal and reduction (a) 350 °C	$MoNi_4$, MoO_{3-x} , $NiMoO_4$, nanorods	2	$\eta_{10} = 17, \eta_{100} = 52, \eta_{500} 1.13 \textcircled{a} \eta_{100} = 114$	$_{00}$ 1.13 (a) η_{100}	36	20 and 30 mA cm $^{-2}$ for total 20 h	52
MoNi ₄ /MoO ₂ @NF	Hydrothermal and reduction @ 500 °C	MoNi ₄ , MoO ₂ , cuboids	0	$\eta_{10}=15,\eta_{200}=44$	$0.4 ext{ (a) } \eta_{50}$	30	2000 CV cycles; 10, 100, 23 and 200 mA cm ^{-2} for total 30 h	, 23
MoNi ₄ /SSW	Precipitation and decomposition	MoO ₂ , MoNi ₄	I	$ \eta_{100} = 63, \eta_{200} = 77, \eta_{500} = 115 (5 M KOH, 353 K), \eta_{1000} = 161 (5 M KOH, 353 K), 353 K) $		40	100 mA cm ⁻² , 18 h, 150 57 mA cm ⁻² , 150 h (5 M KOH, 353 K)	57
MoNi-HS	Hydrothermal and reduction (a) 500 °C	Ni_4Mo , MoO_x , nanosheets	I	$\eta_{10}=38$	I	31.4	$10~{ m mA~cm}^{-2}, 10~{ m h}$	53
$NiMo/MoO_2$	Hydrothermal and reduction (a) 450 °C	MoO_2 , NiMo, nanosheets	12	$\eta_{10}=52$	1.06 @ η_{150}	43.6	$100~{ m mA~cm}^{-2}, 30~{ m h}$	26
NC/NiMo/NiMoO _x /NF	Hydrothermal and reduction (a) 400 °C	Ni_4Mo , MoO_{3-x} , $NiMoO_4$, nanowires	2	$\eta_{10}=29,\eta_{200}=160$	I	46	$179 \mathrm{\ mA\ cm}^{-2}$, $50 \mathrm{\ h}$	54
MoNi ₄ /MoO _{3-x} /NiCo@NF		MoNi ₄ , MoO _{3-x} , NiCo, nanowires	I	$\eta_{10}=33,\eta_{100}=149$	I	34	3000 CV cycles; 20 mA cm ⁻² , 24 h	22
Ni-Mo-O/Ni4Mo@NC	Electrodeposition, calcination, and electrodeposition	Ni₄Mo, nanosheets	ſ	$\eta_{10}=61$	I	66	$10~\mathrm{mA~cm}^{-2}, 15~\mathrm{h}$	24
${\tt NiMoFe@MoO}_2$	Hydrothermal and reduction @ 500 °C	NiMoFe, MoO ₂ , nano-pillars	I	$\eta_{10} = 24, \eta_{100} = 63, \eta_{200} = 83, \eta_{500} = 130$	00	33	10, 100, 200, 100, and 10 mA cm $^{-2}$ for total 140 h	25
$MoNi_4@MoO_{3-x}$	Hydrothermal and reduction (a) 550 °C	$MoNi_4$, MoO_{3-x} , nanorods	5.4	$\eta_{10}=58.6$	I	44.8	$10~{ m mA~cm}^{-2}, 10~{ m h}$	37
NiMo M/O	Hydrothermal and reduction (a) 500 °C	MoNi ₄ , MoO ₂ , nanosheets	I	$\eta_{10}=16,\eta_{50}=50$	I	31.9	$10~{ m mA~cm}^{-2}, 11~{ m h}$	28

in 1 M Electrochemical performances of highly active Ni-Mo-based catalysts with alloy-hydroxide interfaces

Table 2

Electrocatalyst	Synthesis method	Composition and structure	Overpotential (mV) TOF (s^{-1})	$TOF(s^{-1})$	Tafel slope (mV per decade) Stability	Stability	Ref.
$Mo_{0.84}Ni_{0.16} @Ni (OH)_2$	Hydrothermal, reduction (a) 500 °C and electrodenosition	NiMoO ₄ , Mo _{0.84} Ni _{0.16} , Ni(OH)., nanowires	$\eta_{10}=10,\eta_{100}=91$	0.93 @ η_{100}	71	3000 CV cycles; 20 mA cm ⁻² , 100 h	29
$\mathrm{P-Mo-Ni}(\mathrm{OH})_2$	Hydrothermal and low- temperature H ₂ /N ₂ plasma activation	MoNi ₄ , Ni(OH) ₂ , Ni ₃ N, MoNiN, nanosheet	$\eta_{10} = 22, \eta_{100} = 98$	1.325 $@$ η_{50}	80	10 mA cm ⁻² , 100 h, 50 mA cm ⁻² , 50 h	09
Co(OH) ₂ /NiMo CA@CC	Electrodeposition	Ni _x Mo _y , Co(OH) ₂ , nanosheet	$\eta_{10}=30$	I	41	10 mA cm ⁻² , 24 h, 50 mA cm ⁻² , 24 h, 100 mA cm ⁻² , 24 h	61
h-NiMoFe	Hydrothermal and reduction @ 500 °C	MoO_2 , Ni_4Mo , $Fe-(OH)_4-Ni_4$, nanosheet	$ \eta_{10} = 14, \eta_{500} = 74, \\ \eta_{1000} = 97 $	$2 \otimes \eta_{50}$	30.6	200, 600, 1000, and 1500 mA cm $^{-2}$ for total 40 h	50
Ni _{0.33} Mo _{0.67} -900	High-temperature sintering	$Ni_{0.33}Mo_{0.67}, MoO_x,$ $Ni(OH)_2,$ nanosponge	$\eta_{10} = 37, \eta_{1000} = 316$	I	39.2	2 A cm^{-2} , 300 h	62
RANEY®-type NiMo	Atmospheric plasma spraying and activation	MoNi, Mo _{1.08} Ni _{2.93} , Ni(OH) ₂ , nanosponge	$\eta_{200} = 82~(30~\mathrm{wt}\%)$ KOH)	1	36	2 A, 47 days (30 wt% KOH)	63
NiMo/Ni(OH) ₂ /CC	Hydrothermal and electrodeposition	NiMo, Ni $(OH)_2$, nanosheet	$\eta_{10}=132$	I	134.1	$10 \text{ mA cm}^{-2}, 24 \text{ h}$	41
NiMo@Ni $(OH)_2$ MoO $_x$	Electrodeposition	Ni(OH) ₂ , MoO ₃ , MoO ₂ , nanoparticles	$\eta_{100}=160$	ſ	115	10 mA cm^{-2} , 24 h, 100 mA cm ⁻² , 24 h	42

4. Conclusions and perspectives

In this perspective, we systematically summarize the characteristics of structures and components obtained by different synthesis methods in Ni-Mo-based catalysts, and discuss their corresponding relationship with HER performance in detail. It can be found that most of the currently reported highly active Ni-Mo-based catalysts have alloy-oxide or alloy-hydroxide interface structures, as summarized in Tables 1 and 2. According to the logic of synthesis-structure-performance, we discuss the influence of the composition changes of two types of interface structures on HER activity. For the alloy-oxide interfaces, the Ni₄Mo/MoO_r (mixed oxide with the Mo ion valence from +4 to +6) composites produced by electrodeposition or hydrothermal combined with thermal reduction exhibit activities close to that of platinum. For only the alloy or oxide, their activities are significantly lower than that of composite structures, indicating the synergistic catalytic effect of binary components. Interestingly, the HER activity of MoO₂ in acidic and alkaline media is very close, indicating that MoO2 can eliminate the influence of additional water dissociation under alkaline conditions. For the alloy-hydroxide interfaces, the activity of the Ni_xMo_y alloy with different Ni/Mo ratios is greatly improved by constructing heterostructures with hydroxides such as Ni(OH)2 or Co(OH)2. In particular, pure alloys obtained by metallurgy must be activated to produce a layer of mixed $Ni(OH)_2$ and MoO_x on the surface to achieve high activity. Theoretical and experimental studies show that metallic Ni_xMo_y alloys optimize the Gibbs free energy for hydrogen adsorption and MoO_x or Ni(OH)₂ can weaken the HO-H bond of absorbed water to facilitate water dissociation in the hetero-interfaces. Therefore, it can be seen that the activity of Ni-Mo catalysts probably originates from the interfaces of alloy-oxide or alloyhydroxide.

Although NiMo-based catalysts exhibit outstanding HER activity, the dissolvable nature of Mo in alkaline solution results in the poor stability of the NixMov alloy due to the lower oxidation potential of Mo than that of H2. Therefore, controlling the dissolution of Mo species is crucial to improve the stability of NiMo-based catalysts. At present, there are three strategies that have proved effective and can be tried to develop: (1) preparation of the pure phase NiMo alloy with high specific surface area by a metallurgical method; the most stable catalysts reported are almost all treated by high-temperature alloying. Compared with nanoalloys prepared by a low-temperature chemical method, high-temperature alloying is beneficial to improve the compactness and continuity of the catalyst. After electrochemical activation, a layer of Ni(OH)₂ or MoO₂ on the surface is formed, which can not only facilitate the dissociation of water but also provide a protective layer to prevent the dissolution of the Mo element. (2) The formed interface structure is coated with carbon or other conductive oxides or hydroxides; by adsorbing or depositing a layer of carbon precursor molecules on the surface and then carbonizing, an alloy/oxide or alloy/hydroxide interface structure uniformly coated with carbon layer can be obtained. An additional

Perspective **Chemical Science**

protective layer will partially inhibit the dissolution of Mo. (3) Establishment of dynamic dissolution and re-adsorption equilibrium of Mo ions in electrolytes; the literature results reveal that MoO₄²⁻ can be easily dissolved in KOH electrolyte and readsorbed on the surface of the catalyst during the oxygen evolution reaction (OER), which delivers a promoting effect on OER performance.65 Theoretical calculations show that the adsorption of the dimer $Mo_2O_7^{2-}$ can promote the HER activity of metallic Ni.58 Therefore, the dissolution of Mo will be effectively inhibited and the stability of NiMo-based catalysts will be greatly improved through reasonable control of the above three aspects.

Data availability

All data in this perspective were cited from other references.

Author contributions

Z.-L. W. and Y. Y. conceived the topic and structure of the paper. All authors reviewed and contributed to this paper.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the National Natural Science Foundation of China (NSFC) [Grant number 22075201] and the JST-ERATO Yamauchi Materials SpaceTectonics Project (JPMJER2003). This work was performed in part at the Queensland node of the Australian National Fabrication Facility, a company established under the National Collaborative Research Infrastructure Strategy to provide nano and microfabrication facilities for Australia's researchers.

References

- 1 Q. Wang, M. Nakabayashi, T. Hisatomi, S. Sun, S. Akiyama, Z. Wang, Z. Pan, X. Xiao, T. Watanabe, T. Yamada, N. Shibata, T. Takata and K. Domen, Nat. Mater., 2019, 18,
- 2 J. H. Kim, D. Hansora, P. Sharma, J. W. Jang and J. S. Lee, Chem. Soc. Rev., 2019, 48, 1908-1971.
- 3 J. D. Blakemore, R. H. Crabtree and G. W. Brudvig, Chem. Rev., 2015, 115, 12974-13005.
- 4 H. Lyu, T. Hisatomi, Y. Goto, M. Yoshida, T. Higashi, M. Katayama, T. Takata, T. Minegishi, H. Nishiyama, T. Yamada, Y. Sakata, K. Asakura and K. Domen, Chem. Sci., 2019, 10, 3196.
- 5 R. Subbaraman, D. Tripkovic, D. Strmenik, K. C. Chang, M. Uchimura, A. P. Paulikas, V. Stamenkovic and N. M. Markovic, Science, 2011, 334, 1256-1260.
- 6 Y. Zhao, C. Chang, F. Teng, Y. Zhao, G. Chen, R. Shi, G. I. N. Waterhouse, W. Huang and T. Zhang, Adv. Energy Mater., 2017, 7, 1700005.

- 7 T. Ling, T. Zhang, B. Ge, L. Han, L. Zheng, F. Lin, Z. Xu, W. Hu, X. Du, K. Davey and S. Qiao, Adv. Mater., 2019, 31, 1807771.
- 8 H. Zhou, F. Yu, Q. Zhu, J. Sun, F. Qin, L. Yu, J. Bao, Y. Yu, S. Chen and Z. Ren, Energy Environ. Sci., 2018, 11, 2858–2864.
- 9 Y. Chen, Y. Zhang, X. Zhang, T. Tang, H. Luo, S. Niu, Z. Dai, L. Wan and J. Hu, Adv. Mater., 2017, 29, 1703311.
- 10 J. Zhang, T. Wang, P. Liu, Z. Liao, S. Liu, X. Zhuang, M. Chen, E. Zschech and X. Feng, Nat. Commun., 2017, 8, 15437.
- 11 Z. Cao, Q. Chen, J. Zhang, H. Li, Y. Jiang, S. Shen, G. Fu, B. Lu, Z. Xie and L. Zheng, Nat. Commun., 2017, 8, 15131.
- 12 C. Wei, Y. Sun, G. G. Scherer, A. C. Fisher, M. Sherburne, J. W. Ager and Z. J. Xu, J. Am. Chem. Soc., 2020, 142, 7765-7775.
- 13 B. You, Y. Zhang, Y. Jiao, K. Davey and S. Z. Oiao, Angew. Chem., Int. Ed., 2019, 58, 11796-11800.
- 14 T. Zhang, K. Yang, C. Wang, S. Li, Q. Zhang, X. Chang, J. Li, S. Li, S. Jia, J. Wang and L. Fu, Adv. Energy Mater., 2018, 8, 1801690.
- 15 I. K. Mishra, H. Zhou, J. Sun, F. Qin, K. Dahal, J. Bao, S. Chen and Z. Ren, Energy Environ. Sci., 2018, 11, 2246-2252.
- 16 F. Yu, H. Zhou, Y. Huang, J. Sun, F. Qin, J. Bao and Z. Ren, Nat. Commun., 2018, 9, 1-9.
- 17 Z. Wang, J. Chen, E. Song, N. Wang, J. Dong, X. Zhang, P. M. Ajayan, W. Yao, C. Wang, J. Liu, J. Shen and M. Ye, Nat. Commun., 2021, 12, 5960.
- 18 C. Lu, D. Tranca, J. Zhang, F. R. Hernandez, Y. Su, X. Zhuang, F. Zhang, G. Seifert and X. Feng, ACS Nano, 2017, 11, 3933-
- 19 N. Han, K. R. Yang, Z. Lu, Y. Li, W. Xu, T. Gao, Z. Cai, Y. Zhang, V. S. Batista, W. Liu and X. Sun, Nat. Commun., 2018, 9, 924.
- 20 Y. Luo, X. Li, X. Cai, X. Zou, F. Kang, H. M. Cheng and B. Liu, ACS Nano, 2018, 12, 4565-4573.
- 21 Y. Zang, S. Niu, Y. Wu, X. Zheng, J. Cai, J. Ye, Y. Xie, Y. Liu, J. Zhou, J. Zhu, X. Liu, G. Wang and Y. Qian, Nat. Commun., 2019, 10, 1217.
- 22 Q. Wang, Z. L. Zhao, S. Dong, D. He, M. J. Lawrence, S. Han, C. Cai, S. Xiang, P. Rodriguez, B. Xiang, Z. Wang, Y. Liang and M. Gu, Nano Energy, 2018, 53, 458-467.
- 23 J. Zhang, T. Wang, P. Liu, Z. Liao, S. Liu, X. Zhuang, M. Chen, E. Zschech and X. Feng, Nat. Commun., 2017, 8, 15437.
- 24 Z. Jin, L. Wang, T. Chen, J. Liang, Q. Zhang, W. Peng, Y. Li, F. Zhang and X. Fan, Ind. Eng. Chem. Res., 2021, 60, 5145-
- 25 P. Liu, W. Pan, R. Yao, L. Zhang, Q. Wu, F. Kang, H. Fan and C. Yang, J. Mater. Chem. A, 2022, 10, 3760-3770.
- 26 R. B. Patil, S. D. House, A. Mantri, J. C. Yang and J. R. McKone, ACS Catal., 2020, 10, 10390–10398.
- 27 J. Park, H. Kim, G. H. Han, J. Kim, S. J. Yoo, H. J. Kim and S. H. Ahn, J. Mater. Chem. A, 2021, 9, 3677-3684.
- 28 M. Zhou, Y. Zeng, Y. Liu, Y. Sun, F. Lu, X. Zhang, R. Cao, Y. Xue, X. Zeng and Y. Wu, Appl. Surf. Sci., 2022, 597, 153597.
- 29 M. Wang, H. Yang, J. Shi, Y. Chen, Y. Zhou, L. Wang, S. Di, X. Zhao, J. Zhong, T. Cheng, W. Zhou and Y. Li, Angew. Chem., 2021, 133, 5835-5841.

Chemical Science

- 31 J. Song, Y. Q. Jin, L. Zhang, P. Dong, J. Li, F. Xie, H. Zhang, J. Chen, Y. Jin, H. Meng and X. Sun, *Adv. Energy Mater.*, 2021, 11, 2003511.
- 32 J. Cao, H. Li, R. Zhu, L. Ma, K. Zhou, Q. Wei and F. J. Luo, *J. Alloys Compd.*, 2020, **844**, 155382.
- 33 K. Kim, A. P. Tiwari, G. Hyun, Y. Yoon, H. Kim, J. Y. Park, K. An and S. J. Jeon, *J. Mater. Chem. A*, 2021, **9**, 7767–7773.
- 34 A. Nairan, P. Zou, C. Liang, J. Liu, D. Wu, P. Liu and C. Yang, *Adv. Funct. Mater.*, 2019, 29, 1903747.
- 35 D. D. Rodene, E. H. Eladgham, R. B. Gupta, I. U. Arachchige and V. Tallapally, ACS Appl. Energy Mater., 2019, 2, 7112– 7120.
- 36 L. Rößner, H. Schwarz, I. Veremchuk, R. Zerdoumi, T. Seyller and M. Armbrüster, ACS Appl. Mater. Interfaces, 2021, 13, 23616–23626.
- 37 J. Wei, Q. Jia, B. Chen, H. Wang, X. Ke, Y. Dong, G. Liu and Y. Peng, J. Alloys Compd., 2021, 876, 160152.
- 38 M. Fang, W. Gao, G. Dong, Z. Xia, S. Yip, Y. Qin, Y. Qu and J. C. Ho, *Nano Energy*, 2016, 27, 247–254.
- 39 X. Lu, M. Cai, J. Huang and C. Xu, *J. Colloid Interface Sci.*, 2020, **562**, 307–312.
- 40 M. Gong, D. Y. Wang, C. C. Chen, B. J. Hwang and H. Dai, *Nano Res.*, 2016, 9, 28–46.
- 41 C. Li, J. Wang, Y. Wang, J. Li, Z. Yao and Z. Jiang, *ChemistrySelect*, 2020, 5, 6774–6779.
- 42 M. Zhao, E. Li, N. Deng, Y. Hu, C. Li, B. Li, F. Li, Z. Guo and J. He, *Renewable Energy*, 2022, **191**, 370–379.
- 43 Y. Zhou, T. Lin, X. Luo, Z. Yan, J. Wu, J. Wang and Y. Shen, *J. Catal.*, 2020, **388**, 122–129.
- 44 J. M. Jaksič, M. V. Vojnovic and N. V. Krstajic, *Electrochim. Acta*, 2000, 45, 4151–4158.
- 45 J. G. Highfield, E. Claude and K. Oguro, *Electrochim. Acta*, 1999, 44, 2805–2814.
- 46 A. Kawashima, E. Akiyama, H. Habazaki and K. Hashimoto, *Mater. Sci. Eng.*, *A*, 1997, 226, 905–909.
- 47 J. Bau, S. Kozlov, L. Azofra, S. Ould-Chikh, A. Emwas, H. Idriss, L. Cavallo and K. Takanabe, *ACS Catal.*, 2020, **10**, 12858–12866.
- 48 N. Dubouis and A. Grimaud, Chem. Sci., 2019, 10, 9165-9181.

- 49 L. Peng, M. Liao, X. Zheng, Y. Nie, L. Zhang, M. Wang, R. Xiang, J. Wang, L. Li and Z. Wei, *Chem. Sci.*, 2020, 11, 2487–2493.
- 50 Y. Luo, Z. Zhang, F. Yang, J. Li, Z. Liu, W. Ren, S. Zhang and B. Liu, *Energy Environ. Sci.*, 2021, 14, 4610–4619.
- 51 Y. An, X. Long, M. Ma, J. Hu, H. Lin, D. Zhou, Z. Xing, B. Huang and S. Yang, *Adv. Energy Mater.*, 2019, 9, 1901454.
- 52 Y. Y. Chen, Y. Zhang, X. Zhang, T. Tang, H. Luo, S. Niu, Z. H. Dai, L. J. Wan and J. S. Hu, *Adv. Mater.*, 2017, 29, 1703311.
- 53 Y. Zhou, M. Luo, W. Zhang, Z. Zhang, X. Meng, X. Shen, H. Liu, M. Zhou and X. Zeng, ACS Appl. Mater. Interfaces, 2019, 11, 21998–22004.
- 54 J. Hou, Y. Wu, S. Cao, Y. Sun and L. Sun, *Small*, 2017, **13**, 1702018.
- 55 Y. Zhang, G. Yan, Y. Shi, H. Tan and Y. Li, New J. Chem., 2021, 45, 10890–10896.
- 56 L. Yang, H. Liu, Z. Zhou, Y. Chen, G. Xiong, L. Zeng, Y. Deng, X. Zhang, H. Liu and W. Zho, ACS Appl. Mater. Interfaces, 2020, 12, 33785–33794.
- 57 V. Jothi, K. Karuppasamy, T. Maiyalagan, H. Rajan, C. Jung and S. Yi, *Adv. Energy Mater.*, 2020, **10**, 1904020.
- 58 W. Du, Y. Shi, W. Zhou, Y. Yu and B. Zhang, *Angew. Chem., Int. Ed.*, 2021, **60**, 7051–7055.
- 59 X. Lu, M. Cai, Z. Zou, J. Huang and C. Xu, *Chem. Commun.*, 2020, 56, 1729–1732.
- 60 W. Zhang, Y. Tang, L. Yu and X. Y. Yu, *Appl. Catal.*, *B*, 2020, **260**, 118154.
- 61 Q. Zhang, W. Xiao, W. H. Guo, Y. X. Yang, J. L. Lei, H. Q. Luo and N. B. Li, *Adv. Funct. Mater.*, 2021, **31**, 2102117.
- 62 P. Shang, Z. Ye, Y. Ding, Z. Zhu, X. Peng, G. Ma and D. Li, *ACS Sustainable Chem. Eng.*, 2020, **8**, 10664–10672.
- 63 F. Razmjooei, T. Liu, D. A. Azevedo, E. Hadjixenophontos, R. Reissner, G. Schiller, S. A. Ansar and K. A. Friedrich, *Sci. Rep.*, 2020, **10**, 10948.
- 64 R. Subbaraman, D. Tripkovic, K. Chang, D. Strmcnik, A. Paulikas, P. Hirunsit, M. Chan, J. Greeley, V. Stamenkovic and N. Markovic, *Nat. Mater.*, 2012, 11, 550–557.
- 65 H. Liao, X. Zhang, S. Niu, P. Tan, K. Chen, Y. Liu, G. Wang,M. Liu and J. Pan, *Appl. Catal.*, B, 2022, 307, 121150.