

Cite this: *Catal. Sci. Technol.*, 2025,  
15, 2722

## Tailored support reduction of Cu/SrTiO<sub>3</sub> catalysts for enhanced methanol production†

Chiara Pischetola, \*<sup>a</sup> Luca Artiglia, <sup>a</sup>  
Frank Krumeich <sup>b</sup> and Jeroen A. van Bokhoven \*<sup>ab</sup>

Copper supported on strontium titanate is explored as a catalyst in the hydrogenation of carbon dioxide to methanol. We used combined H<sub>2</sub>-TPR, O<sub>2</sub>-TPO, XPS, and STEM-EDX to identify the support defects, tailored by the activation procedure. Strontium titanate forms oxygen vacancies under high-temperature reductive treatments. The extent of its reduction is a function of the copper content and of the pressure; the highest extent is achieved at 2 wt% copper and 20 bar hydrogen. The catalytic data agree with a direct relationship between the methanol selectivity and the concentration of the oxygen vacancies, with the best results being: 90% (10% towards carbon monoxide) and an associated methanol space time yield of 0.49 g<sub>MeOH</sub> g<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>. The selectivity is higher than that achieved on a typical copper catalyst on zinc oxide alumina, while keeping the competitive productivity value, despite having thirty times lower copper content. *Post*-reaction characterisation suggests that these sites are stable under reaction conditions. We propose a dual-site surface mechanism based on oxygen vacancies formed at the copper-support interface and *via* long-distance hydrogen spillover.

Received 10th December 2024,  
Accepted 7th March 2025

DOI: 10.1039/d4cy01487a

rsc.li/catalysis

### Introduction

The current climate crisis calls for the implementation of mitigation strategies based on carbon dioxide (CO<sub>2</sub>) emission reduction, capture and utilization. The methanol (CH<sub>3</sub>OH) economy, postulated by Prof. George A. Olah,<sup>1</sup> is a model of reference for the development of sustainable routes in the chemical and energy sectors. Renewable methanol can be produced *via* (sequestered) carbon dioxide valorisation with green hydrogen (H<sub>2</sub>) according to the equilibrium equation (eqn (1)): CO<sub>2</sub> + 3H<sub>2</sub> ↔ CH<sub>3</sub>OH + H<sub>2</sub>O. The thermodynamic yield of methanol following eqn (1) under energy-efficient (*i.e.*  $T < 250$  °C,  $P < 50$  bar) operations is currently not achievable by the industrial catalyst based on CuO/ZnO/Al<sub>2</sub>O<sub>3</sub> (CZA).<sup>2</sup> This exothermic reaction is hindered by the activation of stable carbon dioxide and its selective conversion into target methanol. In contrast, the competitive formation of carbon monoxide (CO) *via* the endothermic reverse water gas shift (RWGS) reaction

(CO<sub>2</sub> + H<sub>2</sub> ↔ CO + H<sub>2</sub>O; eqn (2)) is thermodynamically favoured under industrial-relevant conditions.

An understanding of the structure–performance relationship common to copper (Cu)-based catalysts can lead to improved catalysts and process optimisation. It is widely accepted<sup>3–5</sup> that the activation of hydrogen and carbon dioxide occurs following a dual-site mechanism. The copper phase accounts for the hydrogen splitting.<sup>6</sup> Regarding the carbon dioxide activation, despite decades-long research in the field,<sup>2,7</sup> the topic is still under debate. Multiple types of active sites have been proposed, notably the copper surface and the Cu–Me alloy<sup>8–10</sup> *vs.* the MeO<sub>*x*–1</sub> oxygen vacancies (OVs)<sup>11–14</sup> at a Cu/MeO<sub>*x*</sub> interface.<sup>15,16</sup> Given the relevance of the CZA catalyst,<sup>2</sup> the Cu/ZnO system has been extensively investigated.<sup>17–19</sup> The CuZn alloy sites, identified as prominent both experimentally<sup>20–22</sup> and from calculations,<sup>23,24</sup> are intertwined with the formation of an oxygen deficient ZnO phase.<sup>25–28</sup> To attempt a rational catalyst design, strategies based on controlled 3D morphologies with adjustable structural features<sup>29,30</sup> have been proposed, highlighting a direct role of ZnO<sub>*x*–1</sub> oxygen vacancies (OVs) in the surface mechanism. A valid approach to confirm, in a systematic manner, the role of oxygen vacancies in the title reaction is to select a reducible support whose metal(s) cannot alloy with copper. Such a material may potentially be a catalyst of interest.

Perovskite SrTiO<sub>3</sub> (STO) well fits this requirement.<sup>31,32</sup> STO has an ABO<sub>3</sub> structure where SrO layers are alternated to those

<sup>a</sup> Center for Energy and Environmental Sciences, Paul Scherrer Institute, Villigen 5232, Switzerland. E-mail: chiara.pischetola@psi.ch

<sup>b</sup> Institute for Chemical and Bioengineering, ETH Zurich, Zurich 8093, Switzerland. E-mail: jeroen.vanbokhoven@chem.ethz.ch

† Electronic supplementary information (ESI) available: Additional details on the catalyst performance indicators (*i.e.* definition and calculations), experimental details and materials characterisation data (H<sub>2</sub>-TPR, O<sub>2</sub>-TPO, XPS, XRD, STEM), including tables with XPS fitting parameters and data analysis (DOC). See DOI: <https://doi.org/10.1039/d4cy01487a>



of TiO<sub>2</sub>. The perovskite reducibility is linked to the formation of oxygen vacancies at the B sites.<sup>33</sup> Metal doping,<sup>34–36</sup> electrochemical reduction,<sup>37,38</sup> plasma treatment<sup>34</sup> and high temperature annealing<sup>39</sup> are common strategies to modulate the OV concentration on ABO<sub>3</sub> perovskites. The presence of a transition metal (*e.g.* copper nanoparticles) on the STO surface could help the support reduction, modulating the required annealing temperature. To date, the only example of carbon dioxide hydrogenation over Cu/SrTiO<sub>3</sub> is the computational work by Hus *et al.*,<sup>40</sup> where kinetic Monte Carlo (KMC) simulations and density functional theory (DFT) calculations showed that methanol production (90% selectivity) is possible in the 200–240 °C temperature range and below 50 bar pressure. A ternary system (Cu–ZnO–SrTiO<sub>3</sub>) has been recently tested in the title reaction and the experimental results suggest a beneficial role of SrTiO<sub>3</sub> in the Cu–ZnO activity in methanol production.<sup>41</sup>

The main goal of this work is to test and characterize a novel system based on copper supported on STO, with controlled properties. The laboratory-synthesised Cu/SrTiO<sub>3</sub> materials are tested in carbon dioxide hydrogenation targeting methanol. We design a strategy to control the STO reduction and study its effect on the methanol productivity. Annealing under a hydrogen flow of catalysts containing different copper loadings and by increasing the hydrogen pressure is demonstrated to be effective in tailoring the extent of STO reduction. Temperature-programmed measurements under reductive (TPR) and/or oxidative (TPO) conditions combined with X-ray photoelectron spectroscopy and electron microscopy analysis shed light on the structure–activity relationships of Cu/STO. Small copper nanoparticles and homogeneously dispersed copper domains formed at high hydrogen pressure allow hydrogen spill-over with the formation of oxygen vacancies beneficial to methanol production. Cu/SrTiO<sub>3</sub> is a catalyst of interest given the high selectivity reached (90%) together with a competitive production level ( $STY_{Cu/SrTiO_3}/STY_{CZA} = 0.83$ ).

## Results

### Catalysis

Fig. 1 and S1† show the time-on-stream response of 1\_STO, 2\_STO, 5\_STO, HP2\_STO and 2\_STO\_C catalysts (see Tables 1 and S1† for specifics) in the continuous gas flow hydrogenation reaction of carbon dioxide at 30 bar and 200 °C. Before the reaction, the catalysts were reduced in hydrogen at 1 bar (20 bar in the case of HP2\_STO). All the catalysts were active towards the production of methanol with carbon monoxide as the only by-product formed from the competitive RWGS reaction. At comparable carbon dioxide conversion levels (4 ± 2%) and under steady state conditions, reached within 30 minutes from the start of the reaction, the methanol selectivity spanned from 23 to 90% following the order: 2\_STO\_C < 1\_STO < 5\_STO < 2\_STO < HP2\_STO.

The trend highlights the fair performance of the Cu catalyst based on commercial SrTiO<sub>3</sub>. A direct comparison

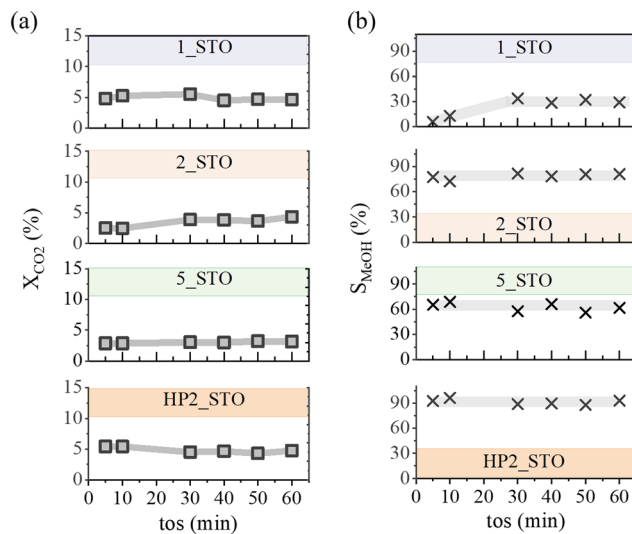


Fig. 1 Flow test response. Time on stream (tos, min) profiles of (a) carbon dioxide conversion ( $X_{CO_2}$ , %) and (b) methanol selectivity ( $S_{MeOH}$ , %) over (from top to bottom) 1\_STO, 2\_STO, 5\_STO and HP2\_STO catalysts, respectively. Reaction conditions:  $P = 30$  bar,  $T = 200$  °C, GHSV = 26 000 h<sup>-1</sup>.

among the tested catalysts is drawn in Fig. 2 by using the methanol space time yield as a metric: in (a) “ $STY_{Cu}$ ” is normalised per copper content and in (b) “ $STY$ ” is normalised with respect to the total catalyst mass. Commercial CZA is used as a reference. Fig. S2† reports the performance correlation plots with the comparison of our data *vs.* the literature. Over the range of temperature (150–250 °C) and pressure (20–60 bar) scanned, the maximum methanol selectivity reached is 80%, at the expense of the corresponding  $STY$ . The striking feature of Fig. 2(a) is that, at comparable conversion levels (see Fig. 1 and S2(c)†), STO-based catalysts outperform commercial CZA. The methanol productivity is non-linearly dependent on copper loading. A volcano-trend is in evidence with the highest value obtained from the catalysts with 2 wt% copper: 2\_STO (by comparing catalysts activated under 1 bar hydrogen) and HP2\_STO (overall). The materials have been engineered to present diversified content of support defects, tailored as oxygen vacancies. Fig. 2(b) shows a positive correlation of the productivity values with the support partial reduction calculated from hydrogen temperature programmed reduction ( $H_2$ -TPR) measurements. Specifically, the extent of support reduction (calculation reported in the Materials and methods section) spans from 0% (2\_STO\_C) to 0.62% (2\_STO) after high-temperature hydrogen activation at 1 bar and increases to 1.63% in the case of the HP2\_STO sample. The dashed line refers to the  $STY$  calculated for commercial CZA showing a value of 0.59 h<sup>-1</sup> with an associated methanol selectivity of 60%. The  $STY$  from SrTiO<sub>3</sub>-based catalysts increases following the order 2\_CML (0.04 g<sub>MeOH</sub> g<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>) < 1\_STO (0.07 g<sub>MeOH</sub> g<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>) < 5\_STO (0.19 g<sub>MeOH</sub> g<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>) < 2\_STO (0.34 g<sub>MeOH</sub> g<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>). The activation of 2\_STO in hydrogen at 20 bar (sample HP2\_STO, dark orange square)



**Table 1** Chemical properties and redox characterisation from H<sub>2</sub>-TPR and O<sub>2</sub>-TPO experiments of copper-supported catalysts on laboratory synthesised SrTiO<sub>3</sub>

Material	Name	Cu content <sup>a</sup> (wt%)	H <sub>2</sub> -TPR experiments		O <sub>2</sub> -TPO experiments <sup>b</sup>	
			Reduction <i>T</i> (°C)	Hydrogen consumed (mmol g <sub>cat</sub> <sup>-1</sup> )	Oxidation <i>T</i> (°C)	Oxygen consumed (mmol <sub>O<sub>2</sub></sub> mmol <sub>X</sub> <sup>-1</sup> )
SrTiO <sub>3</sub>	STO	0	—	0	250	1.60 <sup>f</sup>
Cu/SrTiO <sub>3</sub>	1_STO	1.1	151	0.16	—	—
			157	0.01		
	2_STO	2.0	133	0.06	—	—
			140	0.28		
			146	0.03		
			146 <sup>c</sup>	0.37		
			129 <sup>d</sup>	0.39		
			123 <sup>e</sup>	0.41		
	HP2_STO	— <sup>b</sup>	0	130	0.49 <sup>g</sup>	
	5_STO	5.1	148	0.8	155	—
158			0.02	250	2.18 <sup>f</sup>	


<sup>a</sup> From ICP measurements. <sup>b</sup> Post-reaction. <sup>c</sup> Experiment at 5 bar. <sup>d</sup> Experiment at 10 bar. <sup>e</sup> Experiment at 20 bar. <sup>f</sup> X is STO. <sup>g</sup> X is Cu.

boosts the methanol productivity to the highest recorded value of 0.49 h<sup>-1</sup> with an associated selectivity of 90%. It is important to stress that the STY metric from HP2\_STO is obtained with *ca.* 30 times less Cu content *vs.* CZA.


### Catalyst reducibility

The extent of support reduction is tuned during catalyst activation following high-temperature treatment in hydrogen. H<sub>2</sub>-TPR measurements were performed over fresh bare STO, 1\_STO, 2\_STO, 5\_STO and 2\_STO\_C. The experimental profiles are plotted in Fig. 3, S1 and S3;† while the results from data fitting are listed in Tables 1 and S1.† In the absence of copper, no variation in the TCD response is detected for STO over the 50–250 °C temperature range and at 1 bar overall pressure. A positive peak appears for the Cu-containing materials. The maxima are centred at 145 ± 5 °C

for the samples based on lab synthesised STO, whereas a shift towards higher temperature (190 °C) is observed from the STO\_C support. The increase in copper loading is reflected by larger peak areas (see Fig. S3† and Table 1). However, the calculated hydrogen consumption is not proportional to the mole content of copper; it exceeds the

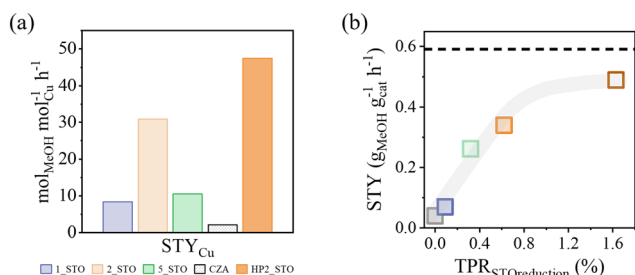

**Fig. 2** Catalytic performances. (a) Commercial CZA, 1\_STO, 2\_STO, 5\_STO and HP2\_STO comparison in terms of the methanol time space yield with respect to the copper content (STY<sub>Cu</sub>, mol<sub>MeOH</sub> mol<sub>Cu</sub><sup>-1</sup> h<sup>-1</sup>). (b) Methanol time space yield (STY, g<sub>MeOH</sub> g<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>) dependence on support partial reduction (TPR<sub>STOreduction</sub>, %); solid (grey (2\_STO\_C), violet (1\_STO), light orange (2\_STO), green (5\_STO)) and open (dark orange, HP2\_STO) symbols indicate catalyst activation at 1 and 20 bar, respectively. The dashed line refers to the STY from CZA (63.5% CuO, 24.7% ZnO, 10.1% Al<sub>2</sub>O<sub>3</sub> and 1.3% MgO). Reaction conditions: *P* = 30 bar, *T* = 200 °C, GHSV = 26 000 h<sup>-1</sup>.

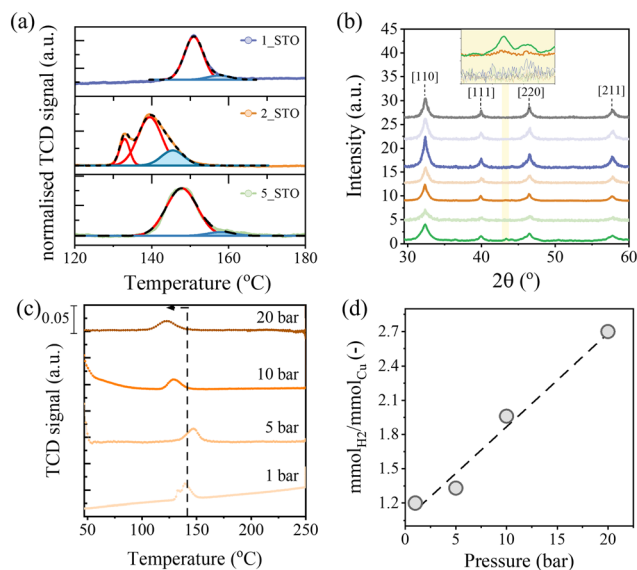

**Fig. 3** Catalytic reducibility. (a) H<sub>2</sub>-TPR peak deconvolution (from top to bottom) of 1\_STO, 2\_STO and 5\_STO. The envelope is given by the dashed black line; the blue areas refer to hydrogen overconsumption with respect to the Cu content. (b) XRD patterns of fresh (light) and *post*-H<sub>2</sub>-TPR (dark) STO (grey), 1\_STO (violet), 2\_STO (orange) and 5\_STO (green) with associated Miller indices from standard SrTiO<sub>3</sub>; the yellow area and the inset highlight the (1 1 1) reflection of metallic Cu. (c) H<sub>2</sub>-TPR profiles of 2\_STO at (from bottom to top): 1 (70 mg<sub>cat</sub>), 5 (46 mg<sub>cat</sub>), 10 (65 mg<sub>cat</sub>) and 20 (45 mg<sub>cat</sub>) bar. (d) Hydrogen overconsumption (%) dependence on total pressure (bar) during H<sub>2</sub>-TPR experiments of the 2\_STO catalyst. The dashed black line is included for visual help.



stoichiometric requirement for the complete copper reduction from Cu(II) to metallic Cu(0) with the only exemption in the case of the 2\_STO\_C sample.


The TCD profiles of 1\_STO and 5\_STO can be fitted with two Gaussian contributions (Fig. 3(a)). The red curves at lower temperature (151 °C and 148 °C, respectively) have an area equivalent to the theoretical hydrogen moles required for complete copper reduction, while the blue curves at higher temperature (157 °C and 158 °C, respectively) close the mass balance. A three-curve fitting is required for 2\_STO where two asymmetrical contributions at low temperature (red curves at 133 °C and 140 °C) have a combined area consistent with the hydrogen requirement for the Cu(II) → Cu(0) transition; such a shape is indicative of non-homogeneous particle size distribution (as further confirmed by microscopy, see *infra*). The blue area at 146 °C represents the excess of hydrogen consumed. The calculated values of support partial reduction from data fitting follow the trend: 2\_STO\_C << 1\_STO < 5\_STO < 2\_STO.

The structural integrity of the materials after the high-temperature treatment is confirmed by comparing the X-ray diffractograms (Fig. 3(b)) of the samples recovered after H<sub>2</sub>-TPR measurements with those collected from the fresh materials. The characteristic reflections of SrTiO<sub>3</sub> (JCPDS No. 35-734) at  $2\theta = 32.5^\circ$ ,  $40.0^\circ$ ,  $46.6^\circ$  and  $57.9^\circ$ , corresponding to the (1 1 0), (1 1 1), (2 2 0) and (2 1 1) planes, respectively, are present in all the patterns; 2\_STO and 5\_STO *post*-H<sub>2</sub>-TPR have an extra peak at  $43.3^\circ$  assigned to the Cu (1 1 1) reflection (JCPDS No. 04-0836). The extent of support reduction in 2\_STO, which showed the highest value from

the experiments at 1 bar, was further tuned by increasing the pressure during H<sub>2</sub>-TPR measurements up to 20 bar. The profiles in Fig. 3(c) gradually shift towards lower reduction temperatures (from 140 to 123 °C) with increasing pressure. The area of the peaks correspond to the hydrogen overconsumption values of Fig. 3(d) which follow a linear positive correlation with respect to the cell pressure.

The following experimental protocol allows us to confirm whether the modifications occurred on the catalysts during activation are preserved after the reaction, thus being relevant to the discussion of the structure–activity relationship of the material. It consists of four *in situ* experiments performed in sequence: (i) H<sub>2</sub>-TPR at 20 bar over 2\_STO to produce HP2\_STO, (ii) carbon dioxide hydrogenation reaction at 30 bar and 200 °C over HP2\_STO, followed by (iii) H<sub>2</sub>-TPR and (iv) oxygen-temperature programmed oxidation (O<sub>2</sub>-TPO) at 1 bar. The results from the *post*-reaction characterisation of HP2\_STO are reported in Fig. 4(a) and Table 1.

A flat TCD response is recorded during H<sub>2</sub>-TPR over the 50–250 °C temperature range. On the other hand, two positive peaks are in evidence in the O<sub>2</sub>-TPO profile. The low-temperature peak appears as a doublet with maxima centred at 130 °C and 155 °C, respectively, whereas the second peak is observed at 250 °C. Peak assignment is done on the basis of the results from O<sub>2</sub>-TPO control experiments on bulk CuO and bare STO (Fig. S4(a)†), which delivered a positive peak at 170 and 250 °C, respectively. Therefore, the first peak in Fig. 4(a) can be attributed to the re-oxidation of the copper phase occurring in a step-wise Cu(0) → Cu(I) → Cu(II) fashion

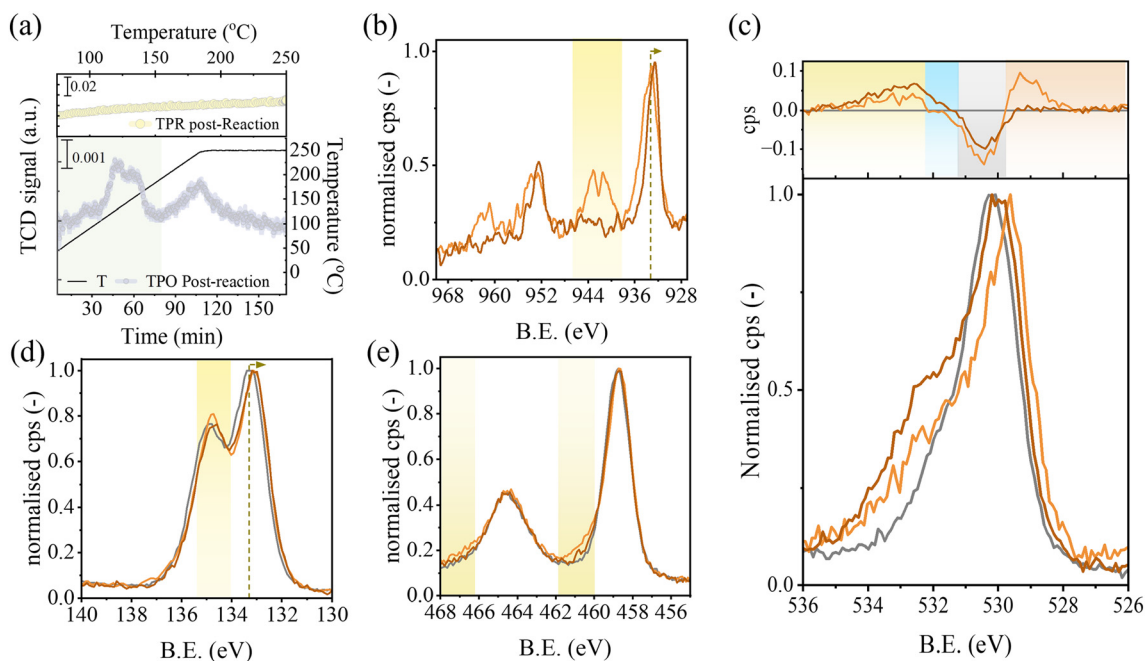

**Fig. 4** *Post*-reaction characterisation. (a) *In situ* O<sub>2</sub>-TPO (bottom panel) and H<sub>2</sub>-TPR (top panel) profiles of HP2\_STO *post*-reaction at 30 bar and 200 °C. (b)–(e) High-resolution photoemission spectra of bare STO (grey), fresh (light orange) 2\_STO and *post*-reaction (dark orange) HP2\_STO samples over the Cu 2p, O 1s, Ti 2p and Sr 3d regions, respectively. The inset in (c) is the area-normalized O 1s profiles of STO, fresh 2\_STO and *post*-reaction HP2\_STO subtracted from the O 1s spectrum of STO.



given the profile shape and total peak area consistent with the reaction stoichiometry (see Table 1). The high-temperature peak can be attributed to the re-oxidation of the support with an oxygen consumption exceeding by 25% the partial reduction extent of HP2\_STO calculated from H<sub>2</sub>-TPR experiments. The oxygen consumption extracted from the high-temperature peak is further analysed in Fig. S4(b),† where the values are normalised with respect to that from bare STO. A linear trend with respect to the support partial reduction from H<sub>2</sub>-TPR experiments is in evidence.

*Ex situ* X-ray photoelectron spectroscopy (XPS) is used to confirm the nature of the reduced species on the catalyst generated by the (designed) hydrogen (over)consumption, namely metallic copper and oxygen vacancies (OVs). The STO (grey), fresh 2\_STO (light orange) and *post*-reaction HP2\_STO (dark orange) materials are examined in Fig. 4(b–e) by comparing the high-resolution photoemission spectra over the Cu 2p (b), O 1s (c), Ti 2p (d) and Sr 3d (e) regions. Peak component data analysis derived from curve fitting is reported in Tables S2 and S3† and in the XPS data analysis section of the ESI.† The Cu 2p signal of 2\_STO reproduces the spectral features of CuO, used as a reference for Cu<sup>2+</sup> (see Fig. S5(a)†). The copper Auger (L<sub>3</sub>M<sub>4.5</sub>M<sub>4.5</sub>) spectrum (Fig. S5(b)†) superimposes well to that of the reference CuO, further proving the presence of Cu<sup>2+</sup>. Moreover, the value of the modified Auger parameter  $\alpha'_{2\_STO} = 1854.3$  eV matches well with that reported for CuO.<sup>42</sup> The Cu 2p spectrum of HP2\_STO shifts towards lower binding energy (BE) values. The main difference between the HP2\_STO and 2\_STO spectra is the quenching of shake-up satellites (see Fig. S5(c)†), suggesting the quantitative reduction of Cu<sup>2+</sup>. The calculated Auger parameter  $\alpha'_{HP2\_STO}$  of 1851.5 eV (*vs.* literature 1849.2 eV of Cu<sub>2</sub>O and 1851.2 eV of Cu<sup>0</sup> (ref. 42)) confirms the presence of metallic copper. However, the line shape of Cu LMM differs from that of bulk metallic copper, taken as a reference in Fig. S5(b)†. The main reasons to explain such a difference are as follows: (i) the reference Cu LMM spectrum for Cu<sup>0</sup> was for foil and not powder, which would better reproduce the large amount of coordinatively unsaturated sites of NPs deposited on the sample; (ii) the broader feature of the spectrum of HP2\_STO reveals the presence of a small fraction of Cu(I) (probably due to partial reoxidation of copper nanoparticles during the sample transfer from the reactor to the XPS setup) in agreement with ref. 43. A direct comparison between the O 1s spectra of STO, 2\_STO and HP2\_STO is provided in the inset of Fig. 4(c), where the area-normalised profile of STO is subtracted from the area-normalised profiles of the other two catalysts; the deconvolution of the O 1s spectrum of HP2\_STO is reported in Fig. S6† as exemplary fitting. The positive feature of 2\_STO at low BE can be attributed to lattice oxygen from CuO supported on the fresh catalyst,<sup>44,45</sup> in agreement with the interpretation of the Cu 2p profiles. The copper nanoparticles on 2\_STO and HP2\_STO attenuate the photoemission signal generated by the lattice oxygen of the STO support resulting in the negative feature of the inset. Unsaturated oxygen atoms adjacent to surface defects like oxygen vacancies<sup>46,47</sup>

are in evidence in the blue spectral region only for HP2\_STO. These defects can form by the overconsumption of hydrogen observed during the H<sub>2</sub>-TPR experiment. Chemisorbed CO<sub>3</sub><sup>2-</sup>,<sup>48,49</sup> OH<sup>-</sup> groups<sup>50,51</sup> and water<sup>52,53</sup> can generate the positive contributions observed at high BE; their relative abundance is: HP2\_STO > 2\_STO > STO. This is consistent with reports correlating the higher content of surface hydroxyls with the higher density of oxygen vacancies *via* reversible repopulation.<sup>54</sup> The Ti 2p and Sr 3d spectra collected from the three materials respectively overlap, with the only differences being as follows. The Ti 2p<sub>1/2</sub> peak broadens towards higher BE ( $\Delta = +1.7$  eV) for 2\_STO, suggesting the presence of a new component (highlighted in yellow in Fig. 4d and shown in Fig. S7(a),† 13.7%). Other Ti 2p<sub>1/2</sub> spectra collected from other CuO/TiO<sub>2</sub> systems<sup>55–57</sup> present as well this feature, which seems to be an effect of doping Cu(II)-oxo species, like on 2\_STO. The presence of mixed Cu–Ti oxides has been invoked as an explanation.<sup>56</sup> *Post*-reduction, copper segregates onto the surface in HP2\_STO; *i.e.* the component at 460.4 eV disappears. A slight negative binding energy shift ( $\Delta = -0.2$  eV) of Sr 3d upon copper deposition is observed. Given the complexity of the materials under investigation, we cannot exclude that such a small shift can arise from energy scale alignment effects. The Sr 3d spectra of 2\_STO and HP2\_STO differ in terms of shape (highlighted in yellow in Fig. 4(e)), where the new feature can be attributed to strontium carbonate (SrCO<sub>3</sub>) at the surface.<sup>58,59</sup> Maximum-normalised XRD patterns of STO, 2\_STO and HP2\_STO in Fig. S8† confirm the presence of strontium carbonate (reflections at  $2\theta = 25.2$  and  $25.9^\circ$ , JCPDS No. 005-0418) in the copper-containing materials.

To summarize, treatment of 2\_STO at high temperature and high pressure in hydrogen (activation step) and hydrogen + carbon dioxide (reaction step) resulted in the *post*-reaction HP2\_STO sample which differs from 2\_STO by: (i) quantitative reduction of Cu<sup>2+</sup> and formation of metallic copper reflected in (ii) the loss of Cu–Ti mixed oxides with copper surface segregation, (iii) formation of OV sites and (iv) lower content of strontium carbonate.

### Catalyst morphology

Conclusive considerations on the structure–activity relationship of the Cu/STO catalysts can be drawn by complementing the description of their electronic properties with structural/morphological characterisation. Adherence of the laboratory synthesised STO materials to the crystallographic structure of SrTiO<sub>3</sub> perovskite is confirmed by XRD (Fig. 3(b)). N<sub>2</sub>-physisorption measurements (Fig. S9(a)†) show a type IV isotherm with an associated H1 hysteresis loop, typical of mesoporous materials arranged as agglomerates. The computed surface area is one order of magnitude higher than that of STO\_C (see Fig. S1(c)†). The representative scanning electron microscopy (SEM) image of STO in Fig. S9(b)† agrees with an agglomerate conformation for the material, revealing hierarchically structured




mesoporous aggregates with a multi-plated morphology (*vs.* the bulk and smooth rod-like structures reported in Fig. S1(c)†). Inductive-coupled plasma (ICP) analysis confirms the nominal copper content on the supported catalysts (see Tables 1 and S1†). The associated BET surface areas differ by a maximum of 5% from that of the bare support.

A morphology study based on transmission electron microscopy (TEM) and scanning transmission electron microscopy (STEM) with energy dispersive X-ray (EDX) spectroscopy was performed on 1\_STO, 2\_STO, and 5\_STO post H<sub>2</sub>-TPR. High-angle annular dark field (HAADF) representative STEM pictures are reported in Fig. S10(a–c)†. The EDX elemental maps of selected areas in Fig. 5 show in green the contributions coming from copper species. The increment of copper loading from 1 to 5 wt% (from (a) to (c)) is reflected by an increase of the counts of spherical-like Cu nanoparticles on top of the support but does not result in a size growth ( $d_{\text{Cu}} = 27 \pm 2$  nm), as shown by the associated particle size distribution in (d–f), thus resulting in a comparable dispersion.<sup>60</sup> Both 1\_STO and 5\_STO follow a standard Gaussian distribution, whereas a bimodal trend is observed for 2\_STO. The bimodal trend in Fig. 5(e) mimics well the TCD profile of Fig. 2(a); a correlation between small copper nanoparticles (7 nm average) and the low-temperature reduction event (133 °C) can be drawn from the collected data. From statistical analysis, at least 85% of copper in 2\_STO is arranged as ill-defined round-shaped nanoparticles (see STEM-EDX and HRTEM images in Fig. S10(d–f)†), but evidence of homogeneous copper distribution with a low concentration over STO is provided in Fig. S11.† In particular, the EDX spectrum in (b), referring to the area in (a), shows two distinct signals with similar intensity at 0.93 and 8.04

keV, which are assigned to the characteristic CuL $\alpha$  and K $\alpha$  lines, respectively.<sup>61</sup> The elemental mapping in (c–f) is characterised by comparable dispersion of the O, Sr, Ti and Cu elements, respectively. The OK $\alpha$ , SrL $\alpha$ , TiK $\alpha$  and K $\beta$  lines appear in Fig. S11(b)† at 0.53, 1.81, 4.51 and 4.95 keV, respectively, in agreement with tabulated values.<sup>61</sup>

## Discussion

The Cu/STO catalysts developed in this study are synergistic systems able to yield methanol. The suboptimal catalytic results of 2\_STO\_C originate from the morphology of the commercial perovskite (see Fig. S1†), unsuitable to be used as an efficient support for Cu nanoparticles. On the other hand, the microstructure of the lab-synthesised STO (Fig. S9†), obtained from confinement effects induced by hydrophobic interactions between the solvents used during synthesis,<sup>32</sup> is key to control the surface properties required for competitive methanol productivity. Given the volcano-type trend of STY<sub>Cu</sub>, one can conclude that the copper phase is not the sole involved in the surface mechanism. Indeed, Fig. 2 suggests that supports with different reduction extents, as a key property, deliver different responses from the activity tests. Recent literature reports making use of Cu–ZnO/SrTiO<sub>3</sub>,<sup>41</sup> Cu/CeO<sub>2</sub> (ref. 62 and 63) and In<sub>2</sub>O<sub>3</sub> (ref. 64 and 65) support the beneficial role of oxygen vacancies (OVs) in methanol synthesis. Nonetheless, the published efforts<sup>29,30,66</sup> have failed so far in providing a system with engineered OVs able to deliver methanol STYs (0.03–0.45 g<sub>MeOH</sub> g<sub>cat</sub><sup>−1</sup> h<sup>−1</sup>, at 220–250 °C and 30–60 bar) matching the productivity from the CZA catalyst (used as a standard for general reference, Fig. S2†). In this work, we

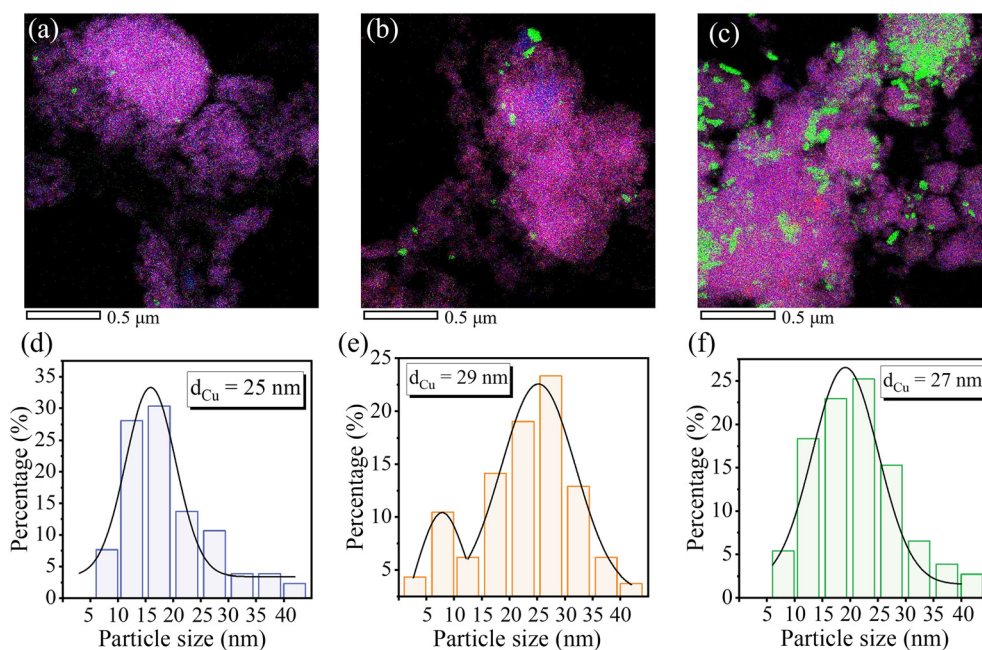


**Fig. 5** Morphological characterisation. (a)–(c) EDX maps of selected areas from 1\_STO, 2\_STO, and 5\_STO post H<sub>2</sub>-TPR with associated (d)–(f) particle size distribution. Note: green areas in (a–c) represent counts from copper species on the Ti + Sr + O overlay given in purple.



succeeded in achieving a competitive STY value vs. CZA, despite having 30 times lower Cu loading, by exploiting the reducibility property of STO. H<sub>2</sub>-TPR analysis combined with surface-sensitive XPS measurements demonstrated that STO redox features can be tailored during the high-temperature hydrogen *pre*-treatment by changing the (i) copper content and (ii) hydrogen pressure. The *in situ* formed metallic copper nanoparticles act as active sites for hydrogen dissociation,<sup>67</sup> which can migrate from the Cu/support interface *via* spill-over and extract lattice oxygen generating vacancies.<sup>68</sup> For a given reducible support, the extent of the spill-over is temperature- and pressure-dependent.<sup>69</sup> Generally speaking, at low hydrogen partial pressure (*e.g.* <10<sup>-1</sup> bar) and high temperature (*e.g.* >150 °C), the support reduction can be limited at the metal/support interface and linked to oxygen consumption *via* water release.<sup>69</sup> As a consequence, samples with a higher Cu/support interface are expected to deliver a greater partial reduction of the support. The values reported in Fig. 2(b), obtained from data fitting (Fig. 3(a), (c), S1(b),† Tables 1 and S1†) agree with the results from the structural and morphological characterisation. No support reduction is calculated for 2\_STO\_C, affected by the lowest Cu dispersion, given its BET surface area. An increasing STO reduction extent is observed from 1\_STO to 5\_STO, where a higher loading (see Table 1), but comparable copper particle size (extracted by microscopy, Fig. 5(d)–(f)), results in more support being in direct contact with copper; thus greater consumption of hydrogen can occur. The 2\_STO sample is an outlier from the trend, being affected by a larger hydrogen overconsumption than expected. This can be attributed to the presence of copper nanoparticles with an average mean diameter equal to 7 nm (*ca.* 20%) which can act as extra (Cu/support) interface sites for STO reduction. The increase in the activation pressure results in higher hydrogen uptake (Table 1) and allows for the hydrogen migration on the surface to occur over a longer distance, thus promoting further support reduction (Fig. 2(b) and 3(d)). The data collected for the Cu/STO system agree with the pressure-dependence study of hydrogen coverage on Pt/TiO<sub>2</sub> by Beck *et al.*<sup>70</sup> and provide experimental proof to the postulated effect of pressure and the support on the distance covered by hydrogen spill-over.<sup>69,71</sup>

H<sub>2</sub>-TPR experiments combined with *operando* XAS on CZA showed that the Cu and Zn speciation is strongly pressure-dependent with reduction events enhanced at increasing pressures.<sup>17</sup> Here, high-temperature (250 °C) and high-pressure (20 bar) hydrogen treatment is used as a successful strategy to form metallic copper and maximise the STO partial reduction. The  $\alpha'_{\text{HP2\_STO}}$  of HP2\_STO is consistent with that of Cu(0), whereas the accounted fraction of Cu(i) from the visual inspection of the Auger line shape in Fig. S5(b)† can originate from the exposure to air of the sample before the *ex situ* analysis.<sup>72</sup> The good correlation between the hydrogen overconsumption (from H<sub>2</sub>-TPR measurements) and the data analysis of the O 1s spectra of STO, 2\_STO and HP2\_STO (Fig. 4(c)) confirms that surface defects, here

identified as oxygen vacancies (OVs), are clearly present only in HP2\_STO. Such OVs are not repopulated during the reaction. Indeed, no further hydrogen is consumed to regenerate them during the *post*-reaction H<sub>2</sub>-TPR experiment, whereas a high temperature oxidizing atmosphere is required to uptake oxygen on the support (Fig. 4(a)). The trend shown in Fig. S4(b)† confirms the dependence of the TCD profile solely on the material structure, excluding any contribution from the (possible still) adsorbed surface intermediates. Reduction at 20 bar of 2\_STO delivered a hydrogen consumption (with respect to the STO phase) that did not match the oxygen uptake during TPO by reduced HP2\_STO (see Table 1). This can be linked to the oxygen uptake ability of STO (Fig. S4(a)† and Table 1), as previously reported in other studies focused on perovskites.<sup>73,74</sup> The excess electrons per OV are transferred to the neighbouring titanium atoms,<sup>75,76</sup> inducing the Ti<sup>4+</sup> → Ti<sup>3+</sup> transition.<sup>39</sup> However, the deconvolution of Ti 2p photoemission spectra in Fig. 4(d) does not allow for the fitting of an extra feature at lower BE than that of Ti<sup>4+</sup>, to account for any Ti<sup>3+</sup>.<sup>36</sup> The exposure to air during sample transfer for the *ex situ* XPS analysis can compromise the stability of Ti<sup>3+</sup> species. Moreover, evidence that oxygen vacancies are formed without the Ti<sup>3+</sup> detection from XPS analysis has been previously reported<sup>77,78</sup> for TiO<sub>2</sub> materials. It was proposed that Ti<sup>3+</sup> species were formed at a sublayer deeper than the probing depth of the XPS analysis.<sup>70,78</sup> DFT computational calculations on Fe-doped SrTiO<sub>3</sub> showed that the energetically favoured configuration when oxygen vacancies are formed is obtained by the sinking of the neighbouring titanium atom into the bulk and the migration of the vacancies towards the surface.<sup>79</sup> This is consistent with the XPS results for O 1s and Ti 2p regions. More experiments with *operando* and bulk-sensitive techniques are required to pinpoint the exact electronic configuration and structure of STO partially reduced materials and exclude any artefacts caused by the *ex situ* characterisation.

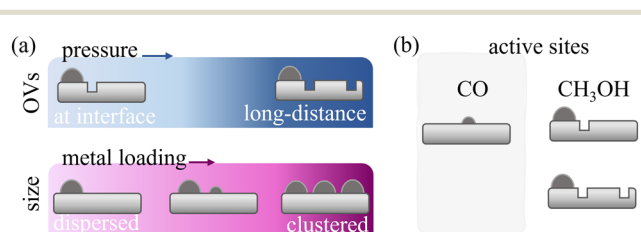

**Scheme 1** Structure–activity relationship. (a) Effect of pressure (blue coded) and metal loading (purple coded) on the type of oxygen vacancy (open square; OVs) and the size of copper nanoparticles (semi-sphere), respectively. Low pressure allows for OV sites to form only at the interface, whereas higher pressures result in longer-distance OV sites. Intermediate loading (2 wt%) results in the simultaneous presence of small and big nanoparticles. (b) Proposed structure–activity relationship between product formation (carbon monoxide and methanol) and the type of active site (small copper nanoparticles, copper nanoparticles + interface OVs and long-distance OVs). The key feature is the conversion at the long-distance OVs of carbon dioxide.



The complex system of active sites (*i.e.* small and big copper nanoparticles, OV<sub>s</sub> at the interface and 'long-distance' OV<sub>s</sub>) on hydrogen-treated Cu/STO materials is summarised in Scheme 1. An educated guess of the structure–activity relationship is proposed. The oxygen vacancies formed at the interface with big copper nanoparticles (common to 1\_STO, 2\_STO and 5\_STO) are adsorption sites for the activation of carbon dioxide.<sup>63</sup> The trend of methanol production in Fig. 1 and 2 suggests that these sites are selective towards the formation of key intermediates involved in the methanol synthesis, as proposed for a Cu/TiO<sub>2-x</sub> defective catalyst.<sup>80</sup> A theoretical study on Cu/STO identified a geometric effect on the carbon monoxide formation rate (*via* RWGS), shown to be enhanced in the presence of small copper nanoparticles.<sup>81</sup> However, the higher  $S_{\text{MeOH}}$  of 2\_STO *vs.* 1\_STO and 5\_STO and of HP2\_STO *vs.* 2\_STO indicates that the long-distance oxygen vacancies (OV<sub>s</sub> as isolated sites or clustered<sup>79</sup>) can act as sites for direct carbon dioxide conversion to methanol. Moreover, combined KMC simulations with DFT calculations on Cu/TiO<sub>2</sub> agreed with the carbon monoxide-mediated pathway as a possible route contributing to methanol production from carbon dioxide hydrogenation.<sup>82</sup> Our system delivers unmatched methanol selectivity (90%) while keeping a productivity value 5 times higher than that of the closest formulation (*i.e.* Cu–ZnO/SrTiO<sub>3</sub> by Liu *et al.*) reported in the literature.<sup>41</sup> In an independent computational study, Hus *et al.*<sup>40</sup> have reported consistent results to our findings.

## Conclusions

Cu/STO catalysts show exceptionally high methanol productivity from carbon dioxide, paving the road for the application of a novel class of methanol catalysts. For the first time, a different formulation than CuO/ZnO/Al<sub>2</sub>O<sub>3</sub> can deliver methanol yields up to industrial standards. High-surface area Cu/STO materials can be synthesised with a tailored number of surface defects, which are identified by combined H<sub>2</sub>-TPR, O<sub>2</sub>-TPO and XPS measurements as oxygen vacancies (OV<sub>s</sub>). The partial STO reduction can occur at the Cu/support interface or at longer distances *via* hydrogen spill-over. The extent of reduction is a function of the dispersion of the copper nanoparticles and of the hydrogen reduction pressure. The OV sites are suggested to play a role in carbon dioxide and carbon monoxide activation. This work shows that such OV<sub>s</sub> are selective sites towards the formation of methanol. The results from our investigation highlight how critical the activation conditions are to tune the desired properties of a given catalyst. Cu/STOs are novel catalysts that can not only be easily engineered but also deliver excellent performances in selectively reducing carbon dioxide to methanol.

## Materials and methods

All the gasses employed in this work (argon, helium, nitrogen, hydrogen, oxygen, hydrogen + carbon dioxide mix)

are of extra-high purity ( $\geq 5.0$ ) from Messer and PanGas. The reagents (strontium carbonate, titanium(IV) butoxide, copper(II) nitrate trihydrate, purity  $\geq 99\%$ ; sodium hydroxide solution,  $>97\%$ ) and solvent (ethylene glycol,  $\geq 99\%$ ) involved in the catalyst(s) synthesis were purchased from Merck. The commercial bulk CuO (Sigma Aldrich, 99%), SrTiO<sub>3</sub> (Sigma Aldrich, 99%) and methanol catalyst CZA (Alfa Aesar, catalogue no. 45776, lot no. I06Z036) were used without further purification.

### Catalyst synthesis

The hydrothermal synthesis of STO was based on the protocol developed by Zhou *et al.*<sup>32</sup> Briefly, strontium carbonate (1.088 g, Sr/Ti = 1.0) was dissolved in 10 mL of deionized water and dropwise added to ethylene glycol (EG) solution containing titanium(IV) butoxide (1.75 g). A sodium hydroxide solution (5 M, 5 mL) was added (total EG:H<sub>2</sub>O = 2 vol/vol) and the mixture was stirred (700 rpm) for 1 h at room temperature. The solution was transferred into an autoclave and thermally treated at 180 °C, 10 °C min<sup>-1</sup> for 24 h. The white powder was collected by centrifugation, washed 3 times with H<sub>2</sub>O + EtOH (50/50 vol) and dried in a vacuum at 70 °C for *ca.* 12 h.

Copper-supported catalysts (2\_STO\_C, 1\_STO, 2\_STO and 5\_STO) were synthesised by a deposition–precipitation method. A copper(II) nitrate aqueous solution was added to the support (300–500 mg), under constant (700 rpm) stirring. The copper concentration was kept constant at 0.10 g L<sup>-1</sup> (for loading of 2 and 5 wt%) and 0.20 g L<sup>-1</sup> (for loading of 1 wt%), as a result of fixed STO/water at  $2.8 \pm 0.2$  g L<sup>-1</sup>. The pH was increased to  $7.8 \pm 3$  by adding dropwise a sodium hydroxide solution (0.1 M) at 80 °C, under reflux. The mixture was aged for 4 h. The precipitate was recovered by centrifugation, washed with H<sub>2</sub>O + EtOH (50/50 vol) until pH = 7 and dried in a vacuum oven at 70 °C for *ca.* 12 h.

### Catalyst characterisation

ICP measurements were performed on an Ultima2 HORIBA Jobin Yvon from the extract in nitric acid/chloric acid (1:3 vol/vol) solution of digested 60–70 mg of sample following a 1:60 dilution. Instrument calibration was performed before each analysis with standard copper solutions over the 0.5–10 ppm range.

H<sub>2</sub>-TPR and O<sub>2</sub>-TPO analyses were carried out using a Micrometrics Autochem 2950 HP unit equipped with a TCD. Samples (*ca.* 40–100 mg) were loaded between two layers of quartz wool inside a quartz (for experiments at  $P = 1$  bar) or stainless steel ( $P > 1$  bar) U-shaped cell. In a standard experiment, a continuous flow of 20 cm<sup>3</sup> min<sup>-1</sup> of 10% vol/vol hydrogen (oxygen) in Ar (He) was fed to the cell while increasing the temperature (2 °C min<sup>-1</sup>) to 250 °C (dwell 1 h); the output passed through a cold trap (*i.e.* isopropanol + liquid nitrogen; -80 °C) before reaching the detector. The profile curve fitting was performed in Origin 2024 employing Gaussian curves after subtracting a non-linear background;



positive peaks are conventionally attributed to (hydrogen or oxygen) gas consumption. The areas from peak deconvolution were converted into hydrogen and oxygen consumption (mmol) on the basis of calibration plots. The extent of the support reduction is defined as the ratio between the moles of hydrogen extracted from the high-temperature peak of H<sub>2</sub>-TPR profiles and the moles of SrTiO<sub>3</sub> used in the experiments.

XRD patterns were collected with a Bruker D8 ADVANCE diffractometer (Bragg–Brentano geometry) under CuK<sub>α</sub> radiation ( $\lambda = 1.54 \text{ \AA}$ , 40 kV and 40 mA) at a scan rate of 0.01° step<sup>-1</sup> over the 4–80° 2 $\theta$  range.

*Ex situ* XPS measurements were carried out in a laboratory XPS setup (base pressure  $9 \times 10^{-9}$  mbar) equipped with a Specs Phoibos 150-EP electron analyzer, using a Mg K<sub>α</sub> non-monochromatic source (excitation energy of 1253.6 eV, pass energy of 20 eV). Powder samples were obtained by pressing 20–30 mg of catalyst powder onto an Ag grid, to obtain thin and homogeneous pellets. The analysis performed on the used catalyst was carried out directly after the reaction, with a transfer time in air (from the cold reactor to the vacuum chamber) within a ten minute range. The full range survey (0–1050 eV BE range), high-resolution spectra of the Sr 3d, Ti 2p, O 1s and Cu 2p core levels and Cu LMM Auger region were collected. The energy scale alignment was obtained using the Ti 2p<sub>3/2</sub> peak (BE = 458.7 eV) as a reference to correct for charging effects. The CasaXPS software (Casa Software Ltd., UK) was used for data treatment. The spectra were fitted using Gaussian–Lorentzian curves after subtracting a Shirley background and by fixing the spin–orbit splitting and the full width at half maximum (FWHM). The modified Auger parameter  $\alpha'$  was calculated as the difference between the KE of the most intense Auger and photoelectron lines of copper plus the excitation energy.

N<sub>2</sub>-physisorption experiments were performed on 3Flex Micromeritics Inc. equipment at 77 K. Prior to analysis, samples were evacuated at 250 °C in a Micromeritics VacPrep 061 system. The specific surface area was calculated according to the Brunauer–Emmett–Teller (BET) method by fitting the isotherms in the 0.02 to 0.1  $p/p_0$  range. The pore volume was determined according to the BLH method.

SEM pictures were taken with a Zeiss Supra VP5 microscope equipped with an FEG electron detector. The materials in the form of fine powder were directly deposited on carbon tape mounted on the sample holder. TEM and STEM-EDX investigation was performed on a JEOL JEM F200 microscope equipped with a high-angle annular dark field detector (HAADF-STEM, 200 kV) and two SDD energy-dispersive X-ray (EDX) detectors. High-resolution TEM (HRTEM) images were recorded with a JEM-ARM300F microscope (GrandARM, JEOL, 300 kV). The sample was prepared by depositing the material dispersed in ethanol on carbon foil supported on the Mo TEM grid. Data analysis was done by using ImageJ software; the distribution of the copper nanoparticles was described by Gaussian fittings based on the counting of 130–260 individuals. The copper nanoparticle

size ( $d_{\text{Cu}}$ ) is given as a surface-weighted mean diameter defined as:  $(\sum_i n_i \times d_i^3) / (\sum_i n_i \times d_i^2)$ , where  $n_i$  is the number of particles of diameter  $d_i$ . Data reproducibility from the characterisation analyses was better than  $\pm 10\%$ .

### Catalytic tests

The Phoenix reactor system unit (ThalesNano) was used for the catalytic tests. The gas phase carbon dioxide hydrogenation reactions were carried out in continuous mode inside a stainless-steel reactor (0.6 cm internal diameter) with a fixed-bed catalyst (250–500  $\mu\text{m}$  fraction) layer reduced *in situ* (20 mL min<sup>-1</sup> hydrogen, 2 °C min<sup>-1</sup> up to 250 °C) prior to each reaction. The catalyst layer consisted of a homogeneous physical mixture of the active catalyst and inert SiC up to a total mass of 0.1 g; this allowed the conversion level to be controlled while keeping the contact time fixed ( $\tau = 0.14$  s). The reactants (*pre*-mixed 24.86 mol% carbon dioxide + 75.14 mol% hydrogen) were delivered with a calibrated mass flow controller at a fixed flow of 50 mL min<sup>-1</sup>. The reactions were performed at 200 °C and 30 bar; blank tests over the empty reactor, SiC fixed-bed and under pure hydrogen flow resulted in undetected carbon dioxide conversion and/or methanol production. The gaseous effluent was analyzed using an on-line micro-GC (Inficon 3000 Micro GC) equipped with a TCD. Isothermal conditions were maintained over molsieve (80 °C, argon carrier) and PlotU (120 °C, helium carrier) columns for the detection of non-polar and polar compounds, respectively. The catalysts performances were evaluated under steady-state conditions (*i.e.* fluctuations of carbon dioxide molar flow of  $\pm 5\%$  with respect to the average value) on the basis of (i) carbon dioxide conversion ( $X_{\text{CO}_2}$ , %), (ii) methanol selectivity ( $S_{\text{MeOH}}$ , %) and (iii) methanol space time yield (STY,  $\text{g}_{\text{MeOH}} \text{g}_{\text{cat}}^{-1} \text{h}^{-1}$ ), *i.e.* catalyst performance indicators, see the ESI† for more details. Carbon mass balance was better than  $\pm 7\%$ .

### Data availability

All the data relevant to the study have been included in the manuscript and as part of the ESI.† The raw data will be provided by the corresponding authors upon request.

### Author contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

### Conflicts of interest

The authors declare no competing financial interest.



## Acknowledgements

The authors acknowledge funding from the Paul Scherrer Institut.

## References

- G. A. Olah, *Angew. Chem., Int. Ed.*, 2005, **44**, 2636–2639.
- A. Beck, M. A. Newton, L. G. A. van de Water and J. A. van Bokhoven, *Chem. Rev.*, 2024, **124**, 4543–4678.
- D. Bianchi, T. Chafik, M. Khalfallah and S. J. Teichner, *Appl. Catal., A*, 1995, **123**, 89–110.
- I. A. Fisher and A. T. Bell, *J. Catal.*, 1998, **178**, 153–173.
- M. D. Rhodes and A. T. Bell, *J. Catal.*, 2005, **233**, 198–209.
- S. Dang, H. Yang, P. Gao, H. Wang, X. Li, W. Wei and Y. Sun, *Catal. Today*, 2019, **330**, 61–75.
- J. Niu, H. Liu, Y. Jin, B. Fan, W. Qi and J. Ran, *Int. J. Hydrogen Energy*, 2022, **47**(15), 9183–9200.
- S. Kuld, C. Conradsen, P. G. Moses, I. Chorkendorff and J. Sehested, *Angew. Chem.*, 2014, **126**, 6051–6055.
- M. Ren, Y. Zhang, X. Wang and H. Qiu, *Catalysts*, 2022, **12**, 403–436.
- M. M.-J. Li, Z. Zeng, F. Liao, X. Hong and S. C. E. Tsang, *J. Catal.*, 2016, **343**, 157–167.
- B. Ouyang, W. Tan and B. Liu, *Catal. Commun.*, 2017, **95**, 36–39.
- D. Ferrah, A. R. Haines, R. P. Galhenage, J. P. Bruce, A. D. Babore, A. Hunt, I. Waluyo and J. C. Hemminger, *ACS Catal.*, 2019, **9**, 6783–6802.
- S. Tada, S. Kayamori, T. Honma, H. Kamei, A. Nariyuki, K. Kon, T. Toyao, K. Shimizu and S. Satokawa, *ACS Catal.*, 2018, **8**, 7809–7819.
- H. Chen, H. Cui, Y. Lv, P. Liu, F. Hao and W. Xiong, *Fuel*, 2022, **314**, 123035.
- J. C. Frost, *Nature*, 1988, **334**, 577–580.
- C. Tisseraud, C. Comminges, T. Belin, H. Ahouari, A. Soualah, Y. Pouilloux and A. Le Valant, *J. Catal.*, 2015, **330**, 533–544.
- A. Beck, M. Zabilskiy, M. A. Newton, O. Safonova, M. G. Willinger and J. A. van Bokhoven, *Nat. Catal.*, 2021, **4**, 488–497.
- A. Urakawa, *Nat. Catal.*, 2021, **4**, 447–448.
- N. J. Divins, D. Kordus, J. Timoshenko, I. Sinev, I. Zegkinoglou, A. Bergmann, S. W. Chee, S. Widrinna, O. Karshioğlu and H. Mistry, *Nat. Commun.*, 2021, **12**, 1435.
- P. Amann, B. Klötzer, D. Degerman, N. Köpfle, T. Götsch, P. Lömker, C. Rameshan, K. Ploner, D. Bikaljevic and H.-Y. Wang, *Science*, 2022, **376**, 603–608.
- J. Nakamura, Y. Choi and T. Fujitani, *Top. Catal.*, 2003, **22**, 277–285.
- T. Fujitani, *J. Jpn. Pet. Inst.*, 2020, **63**, 43–51.
- S. Kuld, M. Thorhauge, H. Falsig, C. F. Elkjaer, S. Helveg, I. Chorkendorff and J. Sehested, *Science*, 2016, **352**, 969–974.
- Y.-F. Shi, P.-L. Kang, C. Shang and Z.-P. Liu, *J. Am. Chem. Soc.*, 2022, **144**, 13401–13414.
- X. Liu, J. Luo, H. Wang, L. Huang, S. Wang, S. Li, Z. Sun, F. Sun, Z. Jiang and S. Wei, *Angew. Chem., Int. Ed.*, 2022, **61**, e202202330 (1–10).
- Z. Li, T. Du, Y. Li, H. Jia, Y. Wang, Y. Song and X. Fang, *Fuel*, 2022, **322**, 124264.
- J. Guo, Z. Luo, G. Hu and Z. Wang, *Greenhouse Gases:Sci. Technol.*, 2021, **11**, 1171–1179.
- J. Wang, G. Li, Z. Li, C. Tang, Z. Feng, H. An, H. Liu, T. Liu and C. Li, *Sci. Adv.*, 2017, **3**, e1701290 (1–10).
- D. Kordus, S. Widrinna, J. Timoshenko, M. Lopez Luna, C. Rettenmaier, S. W. Chee, E. Ortega, O. Karshioğlu, S. Kühl and B. Roldan Cuenya, *J. Am. Chem. Soc.*, 2024, **146**, 8677–8687.
- C. Zhang, L. Wang, Y. Chen, X. He, Y. Song, O. M. Gazit and Z. Zhong, *Chem. Eng. J.*, 2023, **475**, 146102.
- J. Wang, T. Wang, Z. Zhao, R. Wang, C. Wang, F. Zhou, S. Li, L. Zhao and M. Feng, *J. Alloys Compd.*, 2022, **902**, 163865.
- M. Zhou, J. Chen, Y. Zhang, M. Jiang, S. Xu, Q. Liang and Z. Li, *J. Alloys Compd.*, 2020, **817**, 152796.
- S. Carlotto, *Appl. Surf. Sci.*, 2022, **602**, 154376.
- Y. Lu, A. Ma, Y. Yu, R. Tan, C. Liu, P. Zhang, D. Liu and J. Gui, *ACS Sustainable Chem. Eng.*, 2018, **7**, 2906–2910.
- E. A. Rüdiger, *Phys. Chem. Chem. Phys.*, 2021, **13**, 368–384.
- Z. Su, F. Fang, X. Li, W. Han, X. Liu and K. Chang, *J. Colloid Interface Sci.*, 2022, **626**, 662–673.
- Y. Zhu, L. Zhang, B. Zhao, H. Chen, X. Liu, R. Zhao, X. Wang, J. Liu, Y. Chen and M. Liu, *Adv. Funct. Mater.*, 2019, **29**, 1901783 (1–12).
- X. Liu, H. Xie, X. Qu, K. Yu, H. Yin, Q. Song and Z. Ning, *J. Solid State Chem.*, 2021, **302**, 122387.
- H. Trabelsi, M. Bejar, E. Dhahri, M. Sajjeddine, K. Khirouni, P. R. Prezas, B. M. G. Melo, M. A. Valente and M. P. F. Graça, *J. Alloys Compd.*, 2017, **723**, 894–903.
- M. Hus, D. Kopac and B. Likozar, *ACS Catal.*, 2018, **9**, 105–116.
- Y. Liu, X. Wang, Z. Wang, C. Chen, J. Song, L. Zhang, W. Bao, B. Sun, L. Wang and D. Liu, *ACS Catal.*, 2024, **14**, 12610–12622.
- C. D. Wagner, A. V. Naumkin, A. Kraut-Vass, J. W. Allison, C. J. Powell and J. R. Rumble Jr, *The NIST X-Ray Photoelectron Spectroscopy (XPS) Database*, US Department of Commerce, 1991.
- L. Martínez, K. Lauwaet, G. Santoro, J. M. Sobrado, R. J. Peláez, V. J. Herrero, I. Tanarro, G. J. Ellis, J. Cernicharo, C. Joblin, Y. Huttel and J. A. Martín-Gago, *Sci. Rep.*, 2018, **8**, 7250.
- Y. Wang, Y. Lü, W. Zhan, Z. Xie, Q. Kuang and L. Zheng, *J. Mater. Chem. A*, 2015, **3**, 12796–12803.
- K. L. Chavez and D. W. Hess, *J. Electrochem. Soc.*, 2001, **148**, G640 (1–5).
- Y. Tang, H. Shen, J. Cheng, Z. Liang, C. Qu, H. Tabassum and R. Zou, *Adv. Funct. Mater.*, 2020, **30**, 1908223 (1–9).
- J. Yang, S. Hu, Y. Fang, S. Hoang, L. Li, W. Yang, Z. Liang, J. Wu, J. Hu and W. Xiao, *ACS Catal.*, 2019, **9**, 9751–9763.
- J. Stoch and J. Gablankowska-Kukucz, *Surf. Interface Anal.*, 1991, **17**, 165–167.
- N. A. Merino, B. P. Barbero, P. Eloy and L. E. Cadús, *Appl. Surf. Sci.*, 2006, **253**, 1489–1493.



- 50 K. Aravinthkumar, E. Praveen, A. J. R. Mary and C. R. Mohan, *Inorg. Chem. Commun.*, 2022, **140**, 109451.
- 51 M. C. Biesinger, L. W. Lau, A. R. Gerson and R. S. C. Smart, *Appl. Surf. Sci.*, 2010, **257**, 887–898.
- 52 X. Peng, J. Zheng, Y. Zhang and Z. Wang, *Mater. Lett.*, 2022, **309**, 131317 (1–4).
- 53 W. Y. Hernández, M. N. Tsampas, C. Zhao, A. Boreave, F. Bosselet and P. Vernoux, *Catal. Today*, 2015, **258**, 525–534.
- 54 T. J. Frankcombe and Y. Liu, *Chem. Mater.*, 2023, **35**, 5468–5474.
- 55 H. Hou, M. Shang, F. Gao, L. Wang, Q. Liu, J. Zheng, Z. Yang and W. Yang, *ACS Appl. Mater. Interfaces*, 2016, **8**, 20128–20137.
- 56 E. Mańkowska, M. Mazur, J. Domaradzki, P. Mazur, M. Kot and J. I. Flege, *Sensors*, 2023, **23**, 3822–3835.
- 57 M. S. P. Francisco, V. R. Mastelaro, P. A. P. Nascente and A. O. Florentino, *J. Phys. Chem. B*, 2001, **105**, 10515–10522.
- 58 P. A. W. Van der Heide, Q. D. Jiang, Y. S. Kim and J. W. Rabalais, *Surf. Sci.*, 2001, **473**, 59–70.
- 59 B. Ura, J. Trawczyński, A. Kotarba, W. Bieniasz, M. J. Illán-Gómez, A. Bueno-López and F. E. Lopez-Suarez, *Appl. Catal., B*, 2011, **101**, 169–175.
- 60 G. Bergeret and P. Gallezot, *Handbook of Heterogeneous Catalysis*, Wiley-VCH, 2008, vol. 2, pp. 738–765.
- 61 Lawrence Berkeley National Laboratory Database, [https://xdb.lbl.gov/Section1/Table\\_1-2.pdf](https://xdb.lbl.gov/Section1/Table_1-2.pdf), (accessed July 5, 2024).
- 62 R. Singh, K. Tripathi and K. K. Pant, *Fuel*, 2021, **303**, 121289 (1–10).
- 63 W. Wang, Z. Qu, L. Song and Q. Fu, *J. Energy Chem.*, 2020, **40**, 22–30.
- 64 A. Cao, Z. Wang, H. Li and J. K. Nørskov, *ACS Catal.*, 2021, **11**, 1780–1786.
- 65 W. Wang, K. Huo, Y. Wang, J. Xie, X. Sun, Y. He, M. Li, J. Liang, X. Gao, G. Yang, S. Lin, F. Cao, H. Jiang, M. Wu and N. Tsubaki, *ACS Catal.*, 2024, **14**, 9887–9900.
- 66 X. Chang, X. Han, Y. Pan, Z. Hao, J. Chen, M. Li, J. Lv and X. Ma, *Ind. Eng. Chem. Res.*, 2022, **61**, 6872–6883.
- 67 R. Prins, *Chem. Rev.*, 2012, **112**, 2714–2738.
- 68 K. Shun, K. Mori, S. Masuda, N. Hashimoto, Y. Hinuma, H. Kobayashi and H. Yamashita, *Chem. Sci.*, 2022, **13**, 8137–8147.
- 69 A. Beck, D. Kazazis, Y. Ekinci, X. Li, E. A. Müller Gubler, A. Kleibert, M.-G. Willinger, L. Artiglia and J. A. van Bokhoven, *ACS Nano*, 2023, **17**, 1091–1099.
- 70 A. Beck, H. Frey, M. Becker, L. Artiglia, M. G. Willinger and J. A. van Bokhoven, *J. Phys. Chem. C*, 2021, **125**, 22531–22538.
- 71 W. Karim, C. Spreafico, A. Kleibert, J. Gobrecht, J. VandeVondele, Y. Ekinci and J. A. van Bokhoven, *Nature*, 2017, **541**, 68–71.
- 72 N. Jardón-Maximino, M. Pérez-Alvarez, R. Sierra-Ávila, C. A. Ávila-Orta, E. Jiménez-Regalado, A. M. Bello, P. González-Morones and G. Cadenas-Pliego, *J. Nanomater.*, 2018, **2018**, 9512768.
- 73 A. Mroziński, S. Molin, P. Błaszczak, T. Miruszewski, K. Górnicka, J. Karczewski and P. Jasiński, *Int. J. Hydrogen Energy*, 2023, **48**, 35250–35266.
- 74 W. Si, Y. Wang, S. Zhao, F. Hu and J. Li, *Environ. Sci. Technol.*, 2016, **50**, 4572–4578.
- 75 D. A. Muller, N. Nakagawa, A. Ohtomo, J. L. Grazul and H. Y. Hwang, *Nature*, 2004, **430**, 657–661.
- 76 R. Astala and P. D. Bristowe, *Modell. Simul. Mater. Sci. Eng.*, 2001, **9**, 415–422.
- 77 L. Liu, F. Gao, H. Zhao and Y. Li, *Appl. Catal., B*, 2013, **134**, 349–358.
- 78 S. Hoang, S. P. Berglund, N. T. Hahn, A. J. Bard and C. B. Mullins, *J. Am. Chem. Soc.*, 2012, **134**, 3659–3662.
- 79 A. Staykov, H. Téllez, T. Akbay, J. Druce, T. Ishihara and J. Kilner, *Chem. Mater.*, 2015, **27**, 8273–8281.
- 80 C. Zhang, L. Wang, U. J. Etim, Y. Song, O. M. Gazit and Z. Zhong, *J. Catal.*, 2022, **413**, 284–296.
- 81 D. Kopač, B. Likožar and M. Huš, *ACS Catal.*, 2020, **10**, 4092–4102.
- 82 S. Kattel, B. Yan, Y. Yang, J. G. Chen and P. Liu, *J. Am. Chem. Soc.*, 2016, **138**, 12440–12450.

