

Cite this: *Chem. Sci.*, 2022, 13, 12461

All publication charges for this article have been paid for by the Royal Society of Chemistry

# Opening the pathway towards a scalable electrochemical semi-hydrogenation of alkynols via earth-abundant metal chalcogenides†

Kevinjeorjios Pellumbi,<sup>a</sup> Leon Wickert,<sup>‡ab</sup> Julian T. Kleinhaus,<sup>b</sup> Jonas Wolf,<sup>ab</sup> Allison Leonard,<sup>b</sup> David Tetzlaff,<sup>ab</sup> Roman Goy,<sup>c</sup> Jonathan A. Medlock,<sup>c</sup> Kai Junge Puring,<sup>a</sup> Rui Cao,<sup>ib</sup> Daniel Siegmund<sup>ib</sup>\*<sup>ab</sup> and Ulf-Peter Apfel<sup>ib</sup>\*<sup>ab</sup>

Electrosynthetic methods are crucial for a future sustainable transformation of the chemical industry. Being an integral part of many synthetic pathways, the electrification of hydrogenation reactions gained increasing interest in recent years. However, for the large-scale industrial application of electrochemical hydrogenations, low-resistance zero-gap electrolyzers operating at high current densities and high substrate concentrations, ideally applying noble-metal-free catalyst systems, are required. Because of their conductivity, stability, and stoichiometric flexibility, transition metal sulfides of the pentlandite group have been thoroughly investigated as promising electrocatalysts for electrochemical applications but were not investigated for electrochemical hydrogenations of organic materials. An initial screening of a series of first row transition metal pentlandites revealed promising activity for the electrochemical hydrogenation of alkynols in water. The most active catalyst within the series was then incorporated into a zero-gap electrolyser enabling the hydrogenation of alkynols at current densities of up to 240 mA cm<sup>-2</sup>, Faraday efficiencies of up to 75%, and an alkene selectivity of up to 90%. In this scalable setup we demonstrate high stability of catalyst and electrode for at least 100 h. Altogether, we illustrate the successful integration of a sustainable catalyst into a scalable zero-gap electrolyser establishing electrosynthetic methods in an application-oriented manner.

Received 19th August 2022  
Accepted 6th October 2022

DOI: 10.1039/d2sc04647d

rsc.li/chemical-science

## Introduction

Hydrogenation reactions constitute some of the most important transformations in the chemical industry providing modern society with important synthons for the production of pharmaceuticals, fragrances, vitamins and margarines amongst others.<sup>1,2</sup> Despite their large-scale industrial application, the use of molecular hydrogen under elevated pressures and temperatures, as well as the employment of expensive and scarce noble metal catalysts such as Pt or Pd, have made the development of greener alternatives increasingly more important in recent years.<sup>3</sup>

Recently, synthetic pathways *via* electrochemical means are gaining increasing attention as tuneable and sustainable replacement of thermal processes.<sup>4</sup> In addition to their modular and scalable character, electrochemical approaches operate under mild conditions with high atom economy compared to their thermocatalytic counterparts.<sup>5</sup> Regarding hydrogenation reactions in particular, electrochemistry can effectively mitigate safety hazards, transport and storage costs as well as carbon dioxide emissions associated with the supply of highly pressurized dihydrogen.<sup>6,7</sup> In the case of electrosynthesis instead of gaseous H<sub>2</sub>, the solvent, ideally water, acts as the proton source, while the possibility to directly use electrons from renewables enables a sustainable implementation.<sup>8</sup> By carefully tuning the applied potential, temperature and electrolyte, a variety of functional groups such as ketones,<sup>9</sup> aldehydes, esters,<sup>10</sup> olefins,<sup>7</sup> alkynes,<sup>11</sup> nitriles<sup>12</sup> and oximes<sup>13</sup> have been electrochemically hydrogenated in recent years.

Albeit their promising perspective, electrolyzers for the electrochemical hydrogenation (ECH) often still use expensive noble metals such as Pd and Pt, deeming the discovery and implementation of novel and inexpensive alternatives crucial to accelerate the large-scale implementation of this technology.<sup>14</sup> Along this line, transition metal chalcogenide-based electrocatalysts have recently gained interest as cheap and stable

<sup>a</sup>Fraunhofer Institute for Environmental, Safety and Energy Technology UMSICHT, Osterfelder Straße 3, D-46047 Oberhausen, Germany. E-mail: ulf.apfel@umsicht.fraunhofer.de; daniel.siegmund@umsicht.fraunhofer.de

<sup>b</sup>Inorganic Chemistry I, Ruhr University Bochum, Universitätsstraße 150, D-44780 Bochum, Germany. E-mail: ulf.apfel@rub.de; daniel.siegmund@rub.de

<sup>c</sup>DSM Nutritional Products AG, Wurmisweg 576, CH-4303 Kaiseraugst, Switzerland

<sup>d</sup>Key Laboratory of Applied Surface and Colloid Chemistry, Ministry of Education, School of Chemistry and Chemical Engineering, Shaanxi Normal University, Xi'an 710119, China

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2sc04647d>

‡ These authors contributed equally to this work.

alternatives to noble metal electrocatalysts in numerous applications.<sup>15</sup> In case of ECH reactions, a few monometallic sulphur-depleted transition metal chalcogenides such as  $\text{CuS}_x$  and  $\text{CoS}_{2-x}$  and  $\text{Co}_3\text{S}_{4-x}$ , have already shown elevated activity for the ECH of alkynes,<sup>16</sup> unsaturated aldehydes<sup>17</sup> and nitroarenes,<sup>18</sup> respectively. Another class of transition metal chalcogenides that could show great promise for the field of ECH in terms of both catalytic activity as well as facile and rapid scalability are pentlandite (Pn) materials. Our group has shown that depending on the applied electrochemical conditions pentlandite-based electrocatalysts,  $\text{M}_9\text{X}_8$  (M: Fe, Co, Ni; X: S, Se), possess the ability to generate reactive hydride species on the catalytic surface either leading to the generation of hydrogen or promoting the hydrogenation of acetonitrile to ethane.<sup>19,20</sup> Regarding scalability, the synthesis of pentlandite materials has also been established by green and scalable mechanochemical methods<sup>21</sup> revealing further possible perspectives towards an industrial implementation. Most significantly, a crucial advantage of the pentlandite structure over other transition metal chalcogenides is the ability to fine-tune structural and electronic properties of the employed catalysts *via* a plethora of metal (Fe/Co/Ni) and chalcogenide (S/Se) variations.<sup>22–25</sup> Consequently, utilising this stoichiometric flexibility more active pentlandite catalysts for the hydrogen evolution reaction (HER),  $\text{CO}_2$  reduction and oxygen evolution (OER) reaction could be developed in recent years.<sup>21–23,25,26</sup> Overall, this interesting subgroup of multi-functional electrocatalysts demonstrates a combination of ideal properties towards the application in the field of ECH.

Regarding conceivable substrates, we turned our focus to the substrate class of alkynols, globally playing a major role in the fields of vitamins and perfumes.<sup>1</sup> More specifically, in order to investigate the capability of pentlandite catalysts towards ECH, we selected 2-methyl-3-butyn-2-ol (MBY) as a model substrate, which represents the main industrial synthon for vitamin A and E synthesis, reaching annual productions in the scale of thousands of metric tons.<sup>1,27</sup> Currently, the industrial hydrogenation of MBY to the highly desired alkene, 2-methyl-3-buten-2-ol (MBE), is mainly performed in batch-reactors under elevated temperatures and pressures suffering from issues of sustainability. Specifically, the lack of green reductants, employment of Pd-based and Pb-containing catalysts, as well as the necessity for additional purification steps, *e.g.* separation of products from the catalysts, remain key drawbacks of this approach.<sup>1</sup> Similarly, despite the ton-scale production of MBE, the minimization of unwanted over-hydrogenation to 2-methyl-3-buten-2-ol (MBA) or possible side reactions, such as dimerization among others, remain major bottlenecks and key topics of current research of MBY hydrogenation.<sup>28</sup> Furthermore, whilst there have been some reports of a continuous MBY-hydrogenation there is still the need for further improvements.<sup>29</sup> Most notably, despite its industrial importance attempts towards the generation of MBE by the more sustainable electrochemical route remain limited within academic or patent literature, with base metal catalysts being non-existent (Fig. 1).<sup>30</sup>

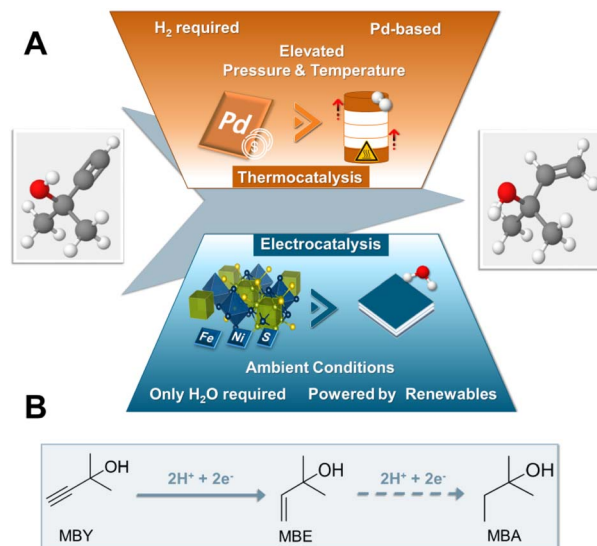


Fig. 1 Schematic representation comparing the current state-of-the-art synthesis of MBY to the herein presented work based on pentlandite electrocatalyst (A). Equation depicting the ongoing hydrogenation processes within the ECH electrolyser (B).

Herein, we report for the first time the electrochemical conversion of MBY (2-methyl-3-butyn-2-ol) to the respective alkene MBE by a PGM-free catalyst in aqueous solution, without the supply of  $\text{H}_2$ . The conversion of this important vitamin synthon is achieved through a series of robust and cheap transition metal chalcogenides based on the pentlandite structure. Going beyond screening experiments, we integrated the most active composition,  $\text{Fe}_3\text{Ni}_6\text{S}_8$ , into industrially relevant zero-gap electrolyzers, reaching yields of 70% for MBE at  $240 \text{ mA cm}^{-2}$  at a cell voltage of 3.0 V, being on par with current noble metal-based electrolyzers, while providing a highly sustainable alternative to the noble-metal-based thermocatalytic state-of-the-art.

## Results and discussion

### Screening of $\text{Fe}_{9-x}\text{Ni}_x\text{S}_8$ –pentlandites for the ECH

Due to our previously gained experiences with this material class, we first focused on already reported materials with variable Ni/Fe ratios ( $\text{Fe}_{9-x}\text{Ni}_x\text{S}_8$ ). This class of catalysts allows us to vary the metal centres without leading to any significant structural changes of the crystal lattice.<sup>22</sup> Following reported synthetic procedures for pentlandite materials, we prepared a series of  $\text{Fe}_{9-x}\text{Ni}_x\text{S}_8$  ( $x = 3–6$ , herein denoted as  $\text{Ni}_x$ ) catalysts, with different Ni/Fe ratios, *via* mechanochemical methods (Fig. S1†).<sup>21</sup> Subsequently, aiming to investigate the intrinsic activity of the  $(\text{Fe},\text{Ni})_9\text{S}_8$  catalysts, the obtained powders were pressed into pellets and mounted into electrodes with the help of a conductive non-catalytically active carbon glue. The polished pellet electrodes ( $\varnothing 3 \text{ mm}$ ,  $A = 0.071 \text{ cm}^2$ ) were used as a working electrode in a three-electrode H-type PEEK cell, possessing a compartment volume of 15 mL (Fig. S2†). To directly probe the activity of our pure pentlandite materials while also



approaching preparative relevant conditions, electrolytic experiments were performed at  $100 \text{ mA cm}^{-2}$  for 2 h. To guarantee sufficient conductivity during testing, our catholyte comprised of 0.3 M KOH and 1 M MBY in water. Notably, the employed reactant as well as the conceivable products are stable under these conditions. All obtained solutions were analysed *via* headspace GC-MS.

Within the investigated series, all tested Pn-materials show good catalytic activity towards ECH in the employed aqueous electrolyte starting from  $\text{Ni}_3$ , possessing a faradaic efficiency for the generation of MBE ( $\text{FE}_{\text{MBE}}$ ) of 28% accompanied by a  $\text{FE}_{\text{MBA}}$  of 10% (Fig. 2B). Transitioning to higher Ni-equivalents, the selectivity towards the ECH increases with  $\text{Ni}_5$  and  $\text{Ni}_6$  showing similarly elevated  $\text{FE}_{\text{MBE}}$  values of 40% at  $100 \text{ mA cm}^{-2}$ , with the remaining percentages corresponding to  $\text{H}_2$  generation as evidenced by gas chromatography. Regarding the observed half-cell potentials, except for  $\text{Ni}_{4.5}$  and  $\text{Ni}_5$ , all of the tested materials demonstrate low half-cell potentials of *ca.*  $-0.5 \text{ V vs. RHE}$  at  $100 \text{ mA cm}^{-2}$  (Fig. 2A).

Inspired by these promising results, we extended our screening and elucidated the role of different metal atoms on the ECH in pentlandites. We subsequently also compared the activity of  $\text{Ni}_6$  with its cobalt analogues,  $\text{Co}_9\text{S}_8$  ( $\text{Co}_9$ ),  $\text{FeCo}_8\text{S}_8$  ( $\text{FeCo}_8$ ), and  $\text{NiCo}_8\text{S}_8$  ( $\text{NiCo}_8$ ), which have been recently synthesized by our group as potential HER-catalysts.<sup>31</sup> Interestingly, transitioning from a Fe/Ni-based system to a Co-based one has a major effect on the observed ECH selectivity. Specifically,  $\text{Co}_9$  shows the lowest activity towards ECH at a  $\text{FE}_{\text{MBE}}$  value of 19%, while the addition of either one equivalent of Ni or Fe leads to an enhancement of the observed ECH activity (Fig. S3†). Specifically,  $\text{FeCo}_8$  enables the production of MBE with a FE of 50%, while  $\text{NiCo}_8$  generates a mixture of hydrogenated products consisting of MBE ( $\text{FE}_{\text{MBE}}$  25%) and MBA ( $\text{FE}_{\text{MBA}}$  18%). Compared to their Ni/Fe-counterparts, Co-based variants also demonstrate a higher half-cell potential with  $\text{FeCo}_8$ , showing the largest value at  $-2.7 \text{ V vs. RHE}$ . These clear differences not only within the  $\text{MCo}_8\text{S}_8$  series but also the different Ni/Fe ratios demonstrate, that small alterations in the composition of our multi-metallic transition metal-rich chalcogenides offer the potential to control the catalytic selectivity and activity for the ECH.

Lastly, to provide a holistic picture within our screening investigation, we compared the activity of our materials to the

performance of monometallic sulphides such as FeS and NiS (Fig. S4†). Although these analogues showed some activity for the conversion of MBY, with NiS showing a  $\text{FE}_{\text{MBE}}$  of 62%, they generally suffered from severe instability under the employed electrocatalytic conditions, a behaviour already observed in reports for the hydrogen evolution reaction.<sup>20</sup> Consequently, the monometallic sulphides were omitted for this investigation.

Since  $\text{Ni}_6$  showed the highest selectivity for the ECH, an elevated MBE:MBA ratio as well as a low half-cell potential within our initial screening (Table S1†), we selected it as our catalyst of choice in further comparisons as well as our following implementation into scalable electrolyzers.

### Implementation of pentlandite materials in zero-gap electrolyzers

Having successfully demonstrated that pentlandite-materials efficiently hydrogenate MBY, we shifted our focus towards achieving a link between catalyst development and implementation in scalable cell designs. In recent years, zero-gap electrolyzers, have shown great promise in electrolytic applications not only for the  $\text{H}_2$  generation or the  $\text{CO}_2$  electroreduction, but also for the ECH.<sup>32</sup> Here, an ion-exchange membrane is pressed in between the porous anode and cathode electrodes. This configuration decreases ohmic resistances, allows for a better control of the reaction environment, facilitates reactant transport, and, more importantly, permits the continuous large-scale operation of such organic transformations.<sup>33</sup>

Focusing on the minimization of noble metals, our investigation mainly employs anion-exchange membranes, allowing for the employment of robust and cost-effective anodes such as Ni-foam for  $\text{O}_2$ -formation. The herein investigated membrane electrode assemblies (MEAs) were implemented into an in-house built zero-gap electrolyser, with an active area of  $12.57 \text{ cm}^2$ , consisting of an anion-exchange membrane sandwiched between a Ni-foam anode and carbon supports coated with sulfidic catalysts on the cathode, respectively (Fig. 3A1–A3 and S5†). During electrolysis, 1 M MBY:0.3 M KOH in  $\text{H}_2\text{O}$  as well as 2 M KOH were used as catholyte and anolyte respectively, with the electrolyte being continuously recirculated while a current density of  $80 \text{ mA cm}^{-2}$  was applied for 2 h. Furthermore, we monitored the substrate and product crossover through the AEM by NMR analysis of both electrolyte compartments (Fig. S6–S9†). The herein discussed results will focus mainly on faradaic efficiencies obtained from the catholyte. The concentration of ECH-products in the anolyte reservoir as well as the respective FE value will only be mentioned when significant crossover was observed.

A key point in our optimization of the ECH in zero-gap electrolyzers is the carbon porous transports layer (PTL) employed in the cathode. Although the role of the PTL has been rigorously investigated in the fields of fuel cells as well as electrolyzers for the  $\text{CO}_2$  reduction or hydrogen generation,<sup>34</sup> in the case of ECH reactions, it currently constitutes an unexplored parameter. To address this issue and optimize the transport of organic substrates to and of the generated products from the active centres,  $\text{Ni}_6$  was airbrushed onto a series of commercially

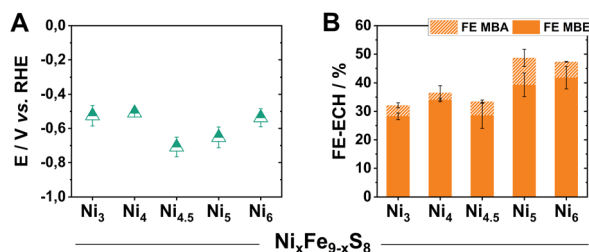
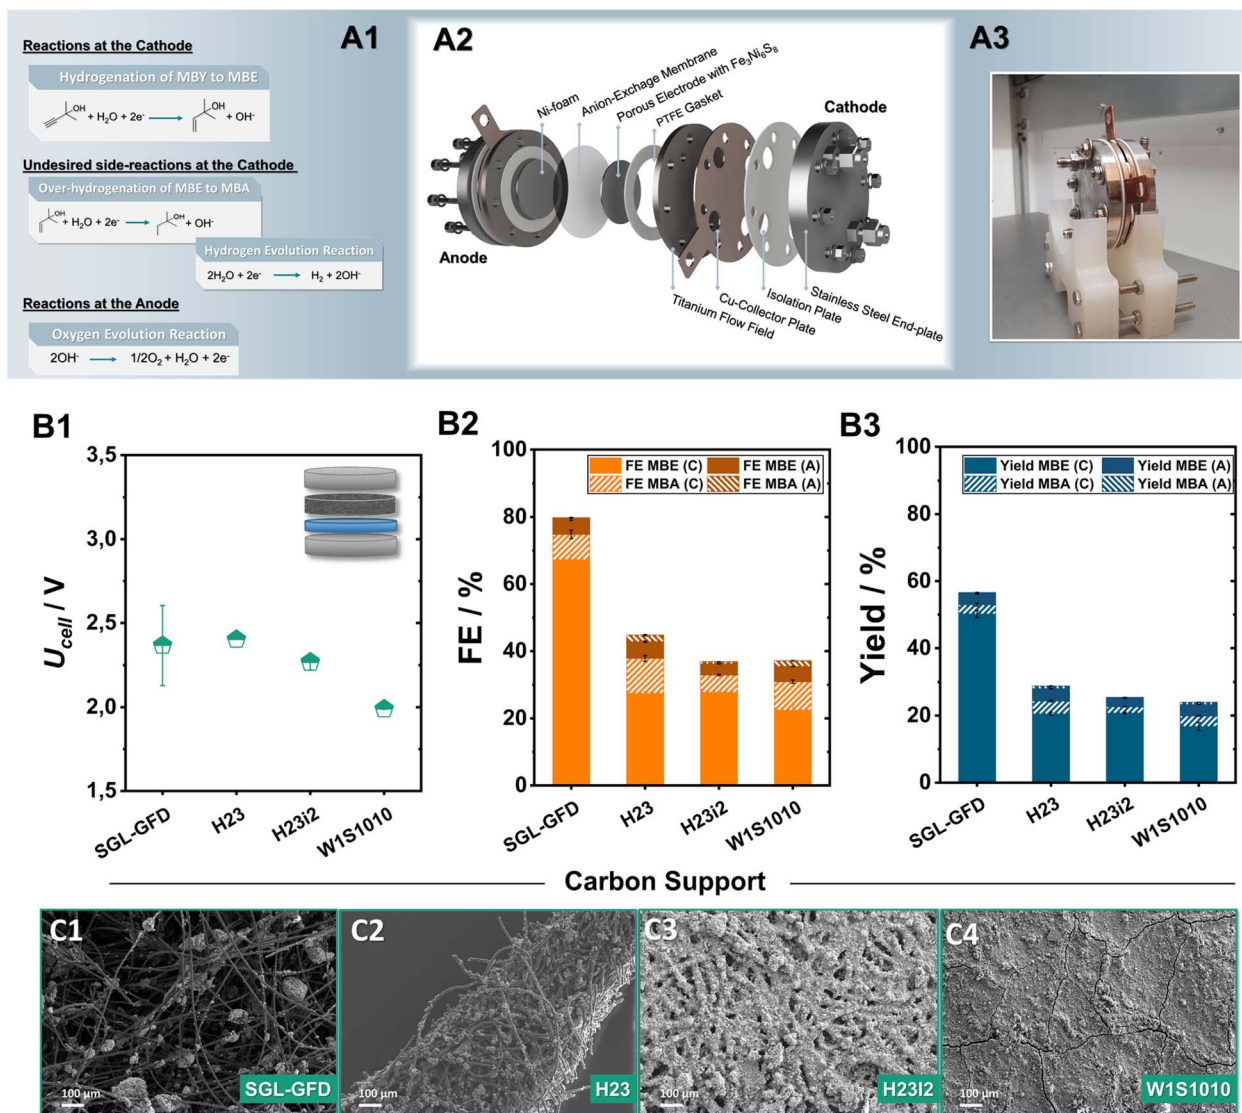


Fig. 2 Half-cell potentials of the herein investigated  $\text{Ni}_x$  pellet electrodes after 2 h of electrolysis at  $100 \text{ mA cm}^{-2}$  (A). The respective faradaic efficiency values *via* GC-MS quantification (B).





**Fig. 3** Reaction schemes of the different half-cell reactions during electrolysis (A1). Schematic representation (A2) and picture of the 12.57 cm<sup>2</sup> electrolyzer employed in this work (A3). Investigation of the role of the employed carbon-support for the semi-hydrogenation of MBY at 80 mA cm<sup>-2</sup> for 2 h of electrolysis. The obtained cell voltage (B1), faradaic efficiency (B2) and yield (B3) through <sup>1</sup>H-NMR quantification. Here, FE<sub>MBX</sub> (C) and FE<sub>MBX</sub> (A) (X: E, A) correspond to the FE values of ECH products detected in the catholyte and anolyte after electrolysis, respectively. Scanning electron microscopy (SEM) analysis of the resulting catalytic layer on SGL-GFD (C1), H23 (C2), H23i2 (C3) and W1S1010 (C4) at a magnification of 100 $\times$ .

available carbon supports; W1S1010, H23, H23i2, and Sigracell GFD 2.5, employing 10 wt% PTFE as a binder. A detailed list of the different PTL properties and vendors can be found in the ESI (Table S2†).

Comparing the two carbon paper substrates H23 and H23i2, it is evident that the hydrophobic treatment plays a minimal role in steering the observed ECH-activity (Fig. 3B2). Both, H23 and its hydrophobically treated counterpart H23i2 demonstrate similar FE<sub>MBE</sub> values, close to 28% alongside the generation of 4% of MBA. The additional implementation of a microporous layer (MPL) accompanied by a hydrophobic treatment in the case of W1S1010 has a negligible effect on the obtained FE<sub>MBE</sub>. Notably, transitioning from traditionally employed carbon paper and cloth materials to a porous carbon felt used in redox-flow

batteries leads to a significant enhancement of the observed ECH activity.<sup>35</sup> Applying a current density of 80 mA cm<sup>-2</sup>, the use of the Sigracell GFD carbon felt (SGL-GFD) as a conductive support, enables the highest activity for the ECH, reaching FE<sub>MBE</sub> values of 67% alongside a FE<sub>MBA</sub> of 8% at a full cell voltage of only 2.4 V, being on par with or outcompeting noble-metal containing MEAs for the ECH.<sup>36</sup> The corresponding yields after 2 h of electrolysis were determined to be 53% for MBE and 3% for MBA in the catholyte, confirming appreciable selectivity for alkene formation with a rate of 0.12 mL<sub>MBE</sub> h<sup>-1</sup> cm<sup>-2</sup> at 80 mA cm<sup>-2</sup> (Fig. 3B3). Regarding crossover of organic products through the membrane by means of either electro-osmosis, or membrane swelling, in the case of all Ni<sub>6</sub>-based carbon electrodes 5% of the total FE<sub>MBE</sub> and 2% of the total FE<sub>MBA</sub>

quantified were detected in the anolyte reservoir after 2 h of electrolysis. Moreover, analysis of the observed gaseous products *via* online GC-MS for the SGL-GFD shows that the remaining FE percentages can be attributed to hydrogen evolution (Fig. S9†).

Analysis of the generated electrodes *via* SEM-EDX reveals that the different carbon supports result in significantly different morphologies of the catalytic layer (Fig. 3C1–C4). As observed by SEM/EDX-measurements (Fig. S10–S15†), W1S1010 carbon cloth, which shows the lowest FE for the ECH in tested series, shows the most compact catalytic layer, possibly due to the existence of a microporous layer (MPL) on the gas diffusion layer (GDL). Moving towards H23 and H23i2 the Ni<sub>6</sub> particles appear to be spread through the surface of the carbon material in the form of spherical agglomerates. Similarly, in case of the SGL-felt, the air-brushed particles are not only located on the upper surface but are also embedded within the 3D structure of the felt forming catalytic clusters on the intersections of the carbon fibres. The formation of these dispersed Ni<sub>6</sub>-PTFE clusters alongside the significantly larger pores of the SGL-GFD could be responsible for the almost doubled activity through better transport of organic reactants and products to and from the catalytic centres.

In addition to the carbon support, the employed binder also plays a key role in tailoring the local environment around the catalytic particles.<sup>37</sup> Therefore, we altered the employed fluoropolymer binder from PTFE to PVDF as well as the added

amount, to identify further tuning points. Overall, both PVDF and PTFE bound electrodes on SGL-GFD show FE values for the ECH of over 50%, with PTFE electrodes outcompeting their polymeric counterparts both in terms of activity for the ECH and specifically for the generation of MBE (Fig. 4B1 and B2). Despite the significantly different FE values, the generated electrodes demonstrate similar cell voltages of 2.5 V independently of the employed binder or added amount. In contrast to the employment of PTFE, which leads to the formation of catalytic cluster on the carbon felt fibres, the use of PVDF leads to a significant engulfment of the catalytic particles by the polymeric binder (Fig. 4A1–A6). The thickness of these PVDF-containing layers, as well as the size of the PTFE-formed clusters, appears to increase with the stepwise addition of the fluoropolymer binder. The observed particle agglomeration could also cause the lower FE values for the ECH at higher binder loadings, since a significant proportion of the catalytic material remains encased in these structures not contributing to the ongoing catalytic processes.

Further attempts to increase the energy efficiency of our process by employing elevated temperatures and thinner ion-exchange membranes did not severely alter the obtained values (Fig. S16†).<sup>14,38</sup> At a cell temperature of 40 °C, the cell voltage decreases by approximately 0.5 V (2.0 V), resulting in similar FE values compared to ambient conditions. The stepwise increase of the operational temperature leads to a steady decrease of the overall ECH activity. This trend could be associated simultaneously with a limited adsorption of the organic substrate on the catalytic surface as well as improved kinetics for the HER under the elevated temperatures.<sup>39</sup> Similarly, employing thinner anion-exchange membranes, of 50 µm and 30 µm thickness (as compared to 130 µm) did not yield any significant improvements in terms of cell voltage, while the total amount of ECH products crossing over to the anolyte increased from 4% (130 µm) to 13% (30 µm), attributed to electroosmosis and membrane swelling.<sup>40</sup>

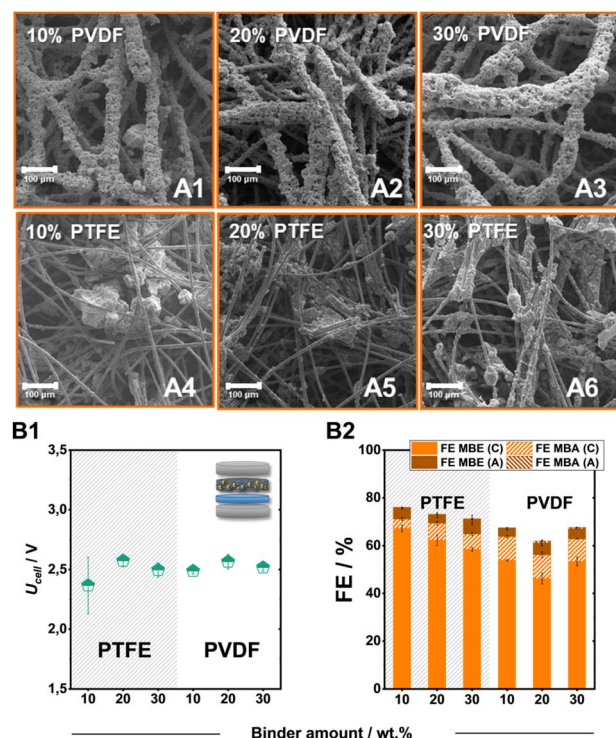


Fig. 4 Scanning electron microscopy (SEM) investigation of PVDF (A1–A3) and PTFE bound electrodes (A4–A6). Effect of the binder nature and content on the ECH of MBY at 80 mA cm<sup>−2</sup>. The obtained cell voltage (B1) and faradaic efficiency (B2). Here, FE<sub>MBX</sub> (C) and FE<sub>MBX</sub> (A) (X: E, A) correspond to the FE values of ECH products detected in the catholyte and anolyte after electrolysis, respectively.

#### Pentlandite electrocatalysts *versus* the current state-of-the art

Comparing the Ni<sub>6</sub>-coated electrodes with commonly used ECH catalysts such as Pd particles (0.35–0.8 µm) or Ni-foam under standard conditions further illustrates the high selectivity of pentlandite materials for the targeted semi-hydrogenation reaction (Fig. 5A1–A3). Specifically, identically prepared Pd-based electrodes show a higher tendency towards the hydrogenation of MBY to MBA (FE<sub>MBA</sub>: 30%) accompanied by a comparatively lower FE<sub>MBE</sub> at similar MBY conversion. In contrast, the integration of Ni-foam as the cathode material demonstrates a decreased activity for the ECH with a total FE-ECH value of just 15%.<sup>8</sup>

By increasing the applied current density to achieve higher product yields, our optimized electrode was able to perform the ECH at elevated current densities of 240 mA cm<sup>−2</sup>, with a maintained FE<sub>MBE</sub> of 30% and a FE<sub>MBE</sub>:FE<sub>MBA</sub> ratio of 7 : 1 (the remaining 70% FE belonging to the formation of H<sub>2</sub>). Even at these elevated current densities, the crossover of organic products to the anode compartment remains at 5%, allowing us

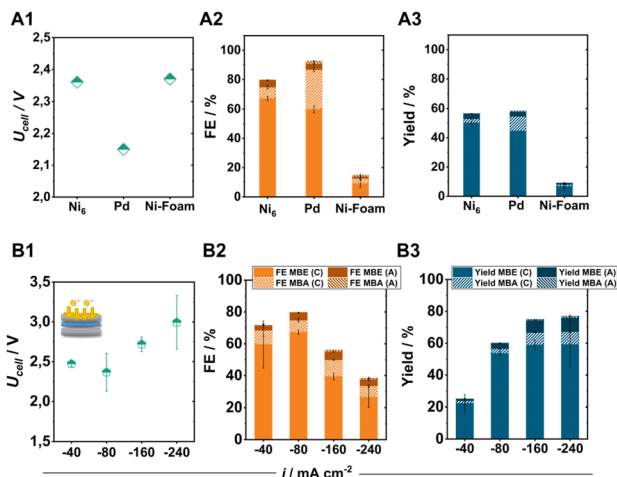


Fig. 5 Comparison of  $\text{Ni}_6$  with the typical electrocatalysts for the ECH, Pd and Ni-foam. The obtained cell voltage (A1), faradaic efficiency (A2), and yield (A3) after 2 h of electrolysis at  $80 \text{ mA cm}^{-2}$ . Effect of the applied current density on the ECH product distribution for  $\text{Ni}_6$ -based electrodes in a zero-gap electrolyser. The obtained cell voltage (B1) faradaic efficiency (B2) and yield (B3) after 2 h of electrolysis at the applied current density. Here,  $\text{FE}_{\text{MBX}}$  (C) and  $\text{FE}_{\text{MBX}}$  (A) (X: E, A) correspond to the FE values of ECH products detected in the catholyte and anolyte after electrolysis, respectively.

to reach a total MBE yield of 70% in 2 h of electrolysis (Fig. 5B3) when combining the generated amounts of MBE in catholyte and anolyte. Regarding cell efficiency, the obtained cell voltages range from 2.4 to 3.0 V depending on the applied current density, demonstrating the capabilities of electrocatalytic anion-exchange-based MEAs to compete with the often PGM-containing cation-exchange variants.<sup>41</sup> Subsequent long-term experiments for 100 h under elevated electrolytic loading, also demonstrate the high stability of pentlandite electrodes (Fig. S17†). Interestingly, although catalyst deactivation is a major issue in thermocatalytic processes, the herein demonstrated elevated stability indicates that ECH reactors could possibly possess a longer lifetime than their counterparts by minimization of by-product formation.

Overall, the observed activity constitutes currently the only example of performing hydrogenation of MBY in aqueous electrolytes without the involvement of any PGM-metals in either cell compartment (Table S3†).

Despite the highly competitive performance of our combined catalyst and electrode optimization in the field of ECH, there is yet still significant room for optimization in direct comparison to thermocatalytic processes. In view of the present results, however, we are confident that the community will be able to establish a green and economically competitive alternative to thermocatalytic processes soon.

## Conclusions

In conclusion, we demonstrate the electrochemical reduction of the alkynol 2-methyl-3-butyne-ol (MBY) to its commercially important semi-hydrogenation product 2-methyl-3-butene-ol (MBE) under industrial relevant conditions using a non-noble

metal catalyst, without the supply of  $\text{H}_2$  gas, in aqueous electrolytes. This important milestone was achieved using cheap and robust transition metal chalcogenides based on the mineral pentlandite ( $\text{M}_9\text{S}_8$ ), further demonstrating the multifunctionality of this material class in a range of reactions such as the ECH, HER,  $\text{CO}_2\text{RR}$  and OER. Moreover, we herein provide a rare example of the utilization of a PGM-free zero-gap electrolyser in an aqueous-based organic reaction. *Via* optimization of the carbon support and binder for the ECH, we were able to reach ECH yields of 70% for the conversion of MBY to MBE after 2 h of electrolysis at  $240 \text{ mA cm}^{-2}$  at cell voltages as low as 3.0 V. We believe that our catalytic and cell parameter screening provide important stepping-stones towards the development of more financially favourable, active and sustainable electrocatalysts for the ECH of substrates beyond alkynols as well as towards the acceleration of this technology in the industrial scale.

## Author contributions

Conceptualization: K. P., J. T. K., K. J. P., D. S. and U.-P. A.; methodology: K. P., L. W., J. T. K., K. J. P., D. S. and U.-P. A.; data curation: K. P., L. W., J. W., A. L. and D. T.; formal analysis: K. P., L. W., J. W., A. L. and D. T.; funding acquisition: U.-P. A. and D. S.; supervision: U.-P. A., K. J. P. and D. S.; writing-original draft preparation: K. P., L. W., J. T. K., R. C., J. M., R. G., U.-P. A. and D. S. All authors have read and agreed to the published version of the manuscript.

## Data availability

Experimental data regarding electrochemical experiments and product analysis are available free of charge in the ESI.†

## Conflicts of interest

These are not conflicts of interest to declare.

## Acknowledgements

K. P. acknowledges the Fonds of the Chemical Industry for a PhD Fellowship. The work of J. T. K. and U.-P. A. was funded by the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation) under Germany's Excellence Strategy – EXC 2033 – 390677874 – RESOLV, the Fraunhofer Internal Programs under Grant no. Attract 097-602175 and the Fraunhofer Lighthouse project ShaPID. D. S. is grateful to BMBF for the financial support within the NanoMatFutur Project “ $\text{H}_2\text{Organic}$ ” No. 03XP0421. The authors are also thankful for support by the Mercator Research Center Ruhr (MERCUR.Exzellenz, ‘DIMENSION’ Ex-2021-0034 and ‘KataSign’ Ko-2021-0016).

## References

- W. Bonrath, J. Medlock, J. Schutz, B. Wustenberg and T. Netscher, in *Hydrogenation*, ed. I. Karamé, IntechOpen, London, 2012, pp. 69–89.





- 2 (a) M. Eggersdorfer, D. Laudert, U. Létinois, T. McClymont, J. Medlock, T. Netscher and W. Bonrath, *Angew. Chem., Int. Ed.*, 2012, **51**, 12960; (b) T. Charvillat, P. Bernardelli, M. Dumas, X. Pannecoucke, V. Ferey and T. Besset, *Chem. Soc. Rev.*, 2021, **50**, 8178; (c) X. Jiang, X. Nie, X. Guo, C. Song and J. G. Chen, *Chem. Rev.*, 2020, **120**, 7984.
- 3 T. H. Meyer, I. Choi, C. Tian and L. Ackermann, *Chem*, 2020, **6**, 2484.
- 4 R. S. Sherbo, A. Kurimoto, C. M. Brown and C. P. Berlinguette, *J. Am. Chem. Soc.*, 2019, **141**, 7815.
- 5 (a) P. Gandeepan, L. H. Finger, T. H. Meyer and L. Ackermann, *Chem. Soc. Rev.*, 2020, **49**, 4254; (b) M. J. Llorente, B. H. Nguyen, C. P. Kubiak and K. D. Moeller, *J. Am. Chem. Soc.*, 2016, **138**, 15110.
- 6 (a) H. B. Goyal, D. Seal and R. C. Saxena, *Renewable Sustainable Energy Rev.*, 2008, **12**, 504; (b) S. A. Akhade, N. Singh, O. Y. Gutiérrez, J. Lopez-Ruiz, H. Wang, J. D. Holladay, Y. Liu, A. Karkamkar, R. S. Weber, A. B. Padmaperuma, M.-S. Lee, G. A. Whyatt, M. Elliott, J. E. Holladay, J. L. Male, J. A. Lercher, R. Rousseau and V.-A. Glezakou, *Chem. J. Rev.*, 2020, **120**, 11370.
- 7 J. Yang, H. Qin, K. Yan, X. Cheng and J. Wen, *Adv. Synth. Catal.*, 2021, **363**, 5407.
- 8 (a) R. S. Delima, M. D. Stankovic, B. P. MacLeod, A. G. Fink, M. B. Rooney, A. Huang, R. P. Jansonius, D. J. Dvorak and C. P. Berlinguette, *Energy Environ. Sci.*, 2022, **15**, 215; (b) Y. He, L. Deng, Y. Lee, K. Li and J.-M. Lee, *ChemSusChem*, 2022, e202200232.
- 9 C. J. Bondue, F. Calle-Vallejo, M. C. Figueiredo and M. T. M. Koper, *Nat. Catal.*, 2019, **2**, 243.
- 10 T. Shono, H. Masuda, H. Murase, M. Shinomura and S. Kashiura, *J. Org. Chem.*, 1992, **57**, 1061–1063.
- 11 (a) Z. Shi, N. Li, H.-K. Lu, X. Chen, H. Zheng, Y. Yuan and K.-Y. Ye, *Curr. Opin. Electrochem.*, 2021, **28**, 100713; (b) B. Li and H. Ge, *Sci. Adv.*, 2019, **5**, eaaw2774.
- 12 (a) R. Mathison and M. A. Modestino, *Chem. Catal.*, 2021, **1**, 246; (b) D. Zhang, J. Chen, Z. Hao, L. Jiao, Q. Ge, W.-F. Fu and X.-J. Lv, *Chem. Catal.*, 2021, **1**, 393.
- 13 A. J. Fry and J. H. Newberg, *J. Am. Chem. Soc.*, 1967, **89**, 6374.
- 14 D. Siegmund, S. Metz, V. Peinecke, T. E. Warner, C. Cremers, A. Grevé, T. Smolinka, D. Segets and U.-P. Apfel, *JACS Au*, 2021, **1**, 527.
- 15 (a) H. M. A. Amin and U.-P. Apfel, *Eur. J. Inorg. Chem.*, 2020, **2020**, 2679; (b) D. Siegmund, N. Blanc, M. Smialkowski, K. Tschulik and U.-P. Apfel, *ChemElectroChem*, 2020, **7**, 1514; (c) M. Nath, H. Singh and A. Saxena, *Curr. Opin. Electrochem.*, 2022, **34**, 100993; (d) X. Shao, X. Zhang, Y. Liu, J. Qiao, X.-D. Zhou, N. Xu, J. L. Malcombe, J. Yi and J. Zhang, *J. Mater. Chem. A*, 2021, **9**, 2526.
- 16 Y. Wu, C. Liu, C. Wang, Y. Yu, Y. Shi and B. Zhang, *Nat. Commun.*, 2021, **12**, 3881.
- 17 S. Han, Y. Shi, C. Wang, C. Liu and B. Zhang, *Cell Rep. Phys. Sci.*, 2021, **2**, 100337.
- 18 Y. Zhao, C. Liu, C. Wang, X. Chong and B. Zhang, *CCS Chem.*, 2021, **3**, 507.
- 19 S. Piontek, K. Junge Puring, D. Siegmund, M. Smialkowski, I. Sinev, D. Tetzlaff, B. Roldan Cuenya and U.-P. Apfel, *Chem. Sci.*, 2019, **10**, 1075.
- 20 B. Konkena, K. Junge Puring, I. Sinev, S. Piontek, O. Khavryuchenko, J. P. Dürholt, R. Schmid, H. Tüysüz, M. Muhler, W. Schuhmann and U.-P. Apfel, *Nat. Commun.*, 2016, **7**, 1.
- 21 D. Tetzlaff, K. Pellumbi, D. M. Baier, L. Hoof, H. Shastri Barkur, M. Smialkowski, H. M. A. Amin, S. Grätz, D. Siegmund, L. Borchardt and U.-P. Apfel, *Chem. Sci.*, 2020, **11**, 12835.
- 22 D. Tetzlaff, K. Pellumbi, K. j. Puring, D. Siegmund, W. S. K. Polet, M. P. Checinski and U.-P. Apfel, *ChemElectroChem*, 2021, **8**, 3161.
- 23 M. Smialkowski, D. Siegmund, K. Pellumbi, L. Hensgen, H. Antoni, M. Muhler and U.-P. Apfel, *Chem. Commun.*, 2019, **55**, 8792.
- 24 M. Smialkowski, D. Siegmund, K. Stier, L. Hensgen, M. P. Checinski and U.-P. Apfel, *ACS Mater. Au*, 2022, **2**(4), 474–481.
- 25 K. Pellumbi, M. Smialkowski, D. Siegmund and U.-P. Apfel, *Chem.–Eur. J.*, 2020, **26**, 9938.
- 26 H. M. A. Amin, M. Attia, D. Tetzlaff and U.-P. Apfel, *ChemElectroChem*, 2021, **8**, 3863.
- 27 (a) G. L. Parker, L. K. Smith and I. R. Baxendale, *Tetrahedron*, 2016, **72**, 1645; (b) S. Kundu and D. Sarkar, *J. Heterocycl. Chem.*, 2021, **58**, 1741.
- 28 (a) N. Semagina and L. Kiwi-Minsker, *Catal. Lett.*, 2009, **127**, 334; (b) L. B. Okhlopko, E. V. Matus, I. P. Prosvirin, M. A. Kerzhentsev and Z. R. Ismagilov, *J. Nanopart. Res.*, 2015, **17**, 1; (c) A. González-Fernández, C. Pischetola, L. Kiwi-Minsker and F. Cárdenas-Lizana, *J. Phys. Chem. C*, 2020, **124**, 3681.
- 29 S. Vernuccio, R. Goy, P. Rudolf von Rohr, J. Medlock and W. Bonrath, *React. Chem. Eng.*, 2016, **1**, 445.
- 30 K. Zhu, J. Ma, L. Chen, F. Wu, X. Xu, M. Xu, W. Ye, Y. Wang, P. Gao and Y. Xiong, *ACS Catal.*, 2022, **12**, 4840.
- 31 M. Smialkowski, D. Tetzlaff, L. Hensgen, D. Siegmund and U.-P. Apfel, *Chin. J. Catal.*, 2021, **42**, 1360.
- 32 (a) K. Nagasawa, Y. Sawaguchi, A. Kato, Y. Nishiki and S. Mitsushima, *Electrochemistry (Tokyo, Jpn.)*, 2018, **86**, 339; (b) H. Liu, T.-H. Lee, Y. Chen, E. W. Cochran and W. Li, *ChemElectroChem*, 2021, **8**, 2817; (c) R. I. Masel, Z. Liu, H. Yang, J. J. Kaczur, D. Carrillo, S. Ren, D. Salvatore and C. P. Berlinguette, *Nat. Nanotechnol.*, 2021, **16**, 118; (d) S. Shiva Kumar and V. Himabindu, *Mater. Sci. Energy Technol.*, 2019, **2**, 442; (e) I. Vincent and D. Bessarabov, *Renewable Sustainable Energy Rev.*, 2018, **81**, 1690.
- 33 (a) B. Gleede, M. Selt, C. Gütz, A. Stenglein and S. R. Waldvogel, *Org. Process Res. Dev.*, 2020, **24**, 1916; (b) C. Gütz, A. Stenglein and S. R. Waldvogel, *Org. Process Res. Dev.*, 2017, **21**, 771; (c) M. M. Hielscher, B. Gleede and S. R. Waldvogel, *Electrochim. Acta*, 2021, **368**, 137420; (d) B. Endrődi, E. Kecsenvity, A. Samu, T. Halmágyi, S. Rojas-Carbonell, L. Wang, Y. Yan and C. Janáky, *Energy Environ. Sci.*, 2020, **13**, 4098; (e) D. A. Salvatore, D. M. Weekes, J. He, K. E. Dettelbach, Y. C. Li, T. E. Mallouk and



- C. P. Berlinguette, *ACS Energy Lett.*, 2018, **3**, 149; (f) L. Hoof, N. Thissen, K. Pellumbi, K. Junge Puring, D. Siegmund, A. K. Mechler and U.-P. Apfel, *Cell Rep. Phys. Sci.*, 2022, **3**, 100825.
- 34 (a) R. Omrani and B. Shabani, *Int. J. Hydrogen*, 2017, **42**, 28515; (b) S. Park, J.-W. Lee and B. N. Popov, *Int. J. Hydrogen*, 2012, **37**, 5850; (c) R. Küngas, *J. Electrochem. Soc.*, 2020, **167**, 44508.
- 35 R. Banerjee, N. Bevilacqua, L. Eifert and R. Zeis, *J. Energy Storage*, 2019, **21**, 163.
- 36 (a) M. Sadakiyo, S. Hata, X. Cui and M. Yamauchi, *Sci. Rep.*, 2017, **7**, 17032; (b) J. Benziger and J. Nehlsen, *Ind. Eng. Chem. Res.*, 2010, **49**, 11052.
- 37 (a) K. Junge Puring, D. Siegmund, J. Timm, F. Möllenbruck, S. Schemme, R. Marschall and U.-P. Apfel, *Adv. Sustainable Syst.*, 2021, **5**, 2000088; (b) T. H. M. Pham, J. Zhang, M. Li, T.-H. Shen, Y. Ko, V. Tileli, W. Luo and A. Züttel, *Adv. Energy Mater.*, 2022, **12**, 2103663.
- 38 R. Krause, D. Reinisch, C. Reller, H. Eckert, D. Hartmann, D. Taroata, K. Wiesner-Fleischer, A. Bulan, A. Lueken and G. Schmid, *Chem. Ing. Tech.*, 2020, **92**, 53.
- 39 (a) Y. Shi, E. Xing, J. Zhang, Y. Xie, H. Zhao, Y. Sheng and H. Cao, *ACS Sustainable Chem. Eng.*, 2019, **7**, 9464; (b) B. Pierozynski and T. Mikołajczyk, *Electrocatalysis*, 2015, **6**, 51.
- 40 A. Gugliuzza, in *Encyclopedia of Membranes*, ed. E. Drioli and L. Giorno, Springer, Berlin, Heidelberg, 2019, pp. 1–2.
- 41 (a) M. C. Leech, A. D. Garcia, A. Petti, A. P. Dobbs and K. Lam, *React. Chem. Eng.*, 2020, **5**, 977; (b) V. Montiel, A. Sáez, E. Expósito, V. García-García and A. Aldaz, *Electrochem. Commun.*, 2010, **12**, 118; (c) A. Sáez, V. García-García, J. Solla-Gullón, A. Aldaz and V. Montiel, *Electrochim. Acta*, 2013, **91**, 69; (d) D. Hoormann, C. Kubon, J. Jörissen, L. Kröner and H. Pütter, *J. Electroanal. Chem.*, 2001, **507**, 215.

