

Nanoscale Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: D. Roy and L. M. Moreau, *Nanoscale Adv.*, 2025, DOI: 10.1039/D5NA00754B.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

Elucidating the Role of Surfactant Structural Parameters on Au Nanoparticle Morphology

Debashree Roy^a and Liane M. Moreau^{*a,b}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

The use of cationic quaternary ammonium halide as a surfactant is popular in aqueous seed-mediated growth methods of noble metal nanoparticles (NPs). Despite the effective shape control of NPs that can be achieved by modifying the surfactant chemistry, these structural parameters have been insufficiently probed. The number of cationic quaternary ammonium halide surfactants explored for the synthesis of Au NPs have been limited primarily to cetyltrimethylammonium bromide (CTAB) and cetyltrimethylammonium chloride (CTAC). In this study, we investigate structural parameters including, headgroup, chain length, and counter-anion of the quaternary ammonium halides, on the resultant Au NPs formed using seed-mediated synthesis. By employing pentatwinned Au NPs as the starting seeds, we observe that i) increasing the bulkiness of the surfactant headgroup results in the formation of Au NPs with fewer stellations and more shape polydispersity, ii) surfactant chain length affects the dimension of Au NPs, and iii) the counter-anion associated with the surfactant affects the Au NP final morphology. These structural parameters provide a practical handle to tune the shape, size, and polydispersity of the final Au NPs.

Introduction. Seed-mediated growth is a versatile synthetic procedure which has resulted in an extensive library of anisotropic Au nanoparticles (NPs) of differing shapes and sizes, bound by both low and high index facets.^{1,2} The easy tunability and reproducibility has become the hallmark of seeded growth, since its inception to synthesize Au nanorods (NRs), one of the most extensively studied anisotropic metal systems.³ The seed-mediated growth comprises of a two-step process wherein “seeds” synthesized in the first step are subjected to overgrowth in the second step.⁴ The separation of heterogeneous nucleation from homogeneous nucleation offers a way to reduce the polydispersity of the NP systems, both in shape and size, the success of which is reflected in the high shape yield associated with the anisotropic Au NPs synthesized using this route.⁵

Much of the success of aqueous seed-mediated synthesis of noble metal NPs has been attributed to the surfactants known to modulate their morphology as a shape-directing agent whilst also acting as capping agents.⁶⁻⁸ The significance of surfactants is not just limited to aqueous seed-mediated synthesis, but other colloidal syntheses of metal NPs as well.^{7,9-11} Here the surfactant chemistry plays a crucial role both during synthesis, by directing anisotropic growth while preventing aggregation of the NPs¹², and post-synthetically influencing the surface functionalization of the NPs, which is expected to have direct consequences in applications ranging from catalysis¹³⁻¹⁸ to drug

delivery¹⁹⁻²¹. Quaternary ammonium halide surfactants commonly used in these syntheses are understood to direct the anisotropic growth of the Au NPs by capping specific facets of the Au NPs and stabilizing them, thereby modulating the growth direction.²² Additionally, the halides present in these surfactants are also known to modify the redox potential of the metal ion apart from providing facet-specific capping.^{5,23-25} These cationic surfactants self-assemble into micelles, above their critical micelle concentration (CMC)- a concentration usually maintained for the synthesis of Au NPs via the aqueous seed-mediated route. The morphological arrangement adopted by cationic surfactants in water can range anywhere from spherical, to cylindrical, to bilayer due to the dependence on the surfactant structure under relevant solution as is evident from numerous prior studies.²⁶⁻³³ Increasing the surfactant concentration gradually leads to the transformation of spherical micelles to cylindrical micelles via coalescence, which eventually leads to the formation of bilayers.³⁴⁻³⁶ This structural transition in micelles take place at higher surfactant concentration as there is an increase in the number density of the counterions due to the dissociation of the surfactants. This increases the ionic strength of the solution, thereby reducing the electrostatic repulsion based on increased water coordination. The direct outcome of this is the increase in the value of the geometrical parameter referred to as the critical packing parameter (CPP). This parameter regulates the surfactant behaviour in the solution where a larger CPP value is associated with lesser curvature of the micellar aggregates.^{35,36} Two widely accepted mechanisms of surfactant arrangement on Au NPs are the formation of micelles and closed bilayers.^{22,37} These studies which are mostly focused on Au NRs,³⁸⁻⁴¹ have confirmed the formation of a cetyltrimethylammonium

^a Department of Chemistry, Washington State University, Pullman, WA 99164.^b Department of Chemistry, University of Wyoming, Laramie, WY 82071

† Supplementary Information available: [Additional SEM images along with NMR, and SAXS data supporting this manuscript have been included]. See DOI: 10.1039/x0xx00000x




bromide (CTAB) bilayer with a thickness between 30–34 Å,⁴² where the outer layer has been found to be in equilibrium with the free surfactants in solution⁴³. Even within individual particles, the surfactant density has been found to vary, with higher density of surfactant at the sides and a significantly reduced surfactant density at the tips of the Au NR.⁴⁴ On the other hand, formation of patchy or discrete globular micelles has been reported for cetyltrimethylammonium chloride⁴⁵ (CTAC) which corroborates well to the poor shape yield of Au NRs associated with CTAC. Additionally, the micellar packing around the Au NP surface has been observed to be altered in the presence of additives/co-surfactants affecting the product yield.^{46–50} Based on these aforementioned observations, it can be inferred that small changes to the structural attributes of the surfactant can have larger implications on the micellar morphologies and their organization on the Au NP surface, affecting the final resulting Au NP morphology.

Previous studies have found a direct correlation between increasing surfactant chain length and increasing NP size for NPs synthesized both photochemically as well as under aqueous conditions.^{51, 52} Still other studies have observed significantly altered morphologies upon changing the alkyl chain length of quaternary ammonium halide based surfactants^{53, 54}. Different studies investigating the effect of surfactant headgroup concluded that the presence of bulkier headgroup slowed the precursor reduction rate enabling better morphological control.^{53, 55–57} The role of the counterion in the quaternary ammonium halide based surfactants has been examined previously in Au NP syntheses resulting in entirely different morphologies despite changing the halide species.^{23, 58–61} The addition of co-surfactants provides even greater tunability in NP morphology. For example, modifying the chain length of a co-surfactant in a binary mixture of quaternary ammonium halide-based surfactants has been observed to affect the yield and dimension of Au NRs.^{62–64} In the cases of both single and co-surfactant systems associated with quaternary ammonium halide-based surfactants commonly employed in the aqueous seed-mediated synthesis of noble metal NPs, their structural parameters associated with anisotropic growth have never been studied in detail before through a thorough systematic investigation.

The formation of two distinct morphologies (pentatwinned NRs and decahedra) in the presence of two surfactants CTAB and benzyldimethylhexadecylammonium chloride (BDAC) which differ in their respective counter anion and polar head groups show that the pentatwinned seeds are more susceptible to structural parameter changes of the surfactant.^{65, 66} This makes the pentatwinned seeds ideal candidates to undertake an investigation to study the effect of structural parameters associated with quaternary ammonium halides. Additionally, the propensity of single crystalline seeds to result in Au NRs in presence of bromide and Ag⁺ also makes it difficult to study other structural parameters associated with these quaternary ammonium halides.^{67–69}

In the present work, we investigate the dependence of the structural parameters associated with the quaternary ammonium halide surfactants to the resultant Au NP

morphology at concentrations much higher than their CMC, mimicking concentration typically maintained for seed-mediated aqueous synthesis. The quaternary ammonium halide-based surfactants are a class of cationic surfactants whose structural parameters can be divided into three segments—the polar headgroup, the non-polar hydrocarbon chain acting as the tail, and the halide counter anion associated with the headgroup.⁶ Because of solubility and stability issues, these cationic surfactants are mostly available in their chloride and bromide forms only. To examine the effect of the polar headgroup, we studied the C₁₆TAC analogues, CTAC, cetylpyridinium chloride (CPC), and BDAC with different headgroups, while the length of the non-polar hydrocarbon chain and the chloride counterion were unchanged. This allowed us to understand the steric effect associated with the headgroup in modifying the final NP. We found that increasing the bulkiness of the headgroup resulted in Au NPs with lesser branching and narrower arms and more shape polydispersity. To understand how changing the surfactant counterion would affect the growth of pentatwinned seeds, both C₁₆TAX and C₁₆PX (X = Cl/Br) surfactants were explored in the syntheses. The chloride-based surfactants resulted in stellated morphologies; however, no defined morphology could be assigned to the Au NPs generated from the corresponding bromide counterparts. The chain length of the surfactant not only determines the hydrophobicity of the surfactant but is also crucial for interchain packing of the surfactant bilayer on the Au surface.⁷⁰ Thus, when the pentatwinned seeds were subjected to growth in presence of surfactants (C₁₆-BDAC vs C₁₄-BDAC) which varied only in the hydrocarbon chain length, the dimension of the of the Au NPs was affected more than the resultant morphology.

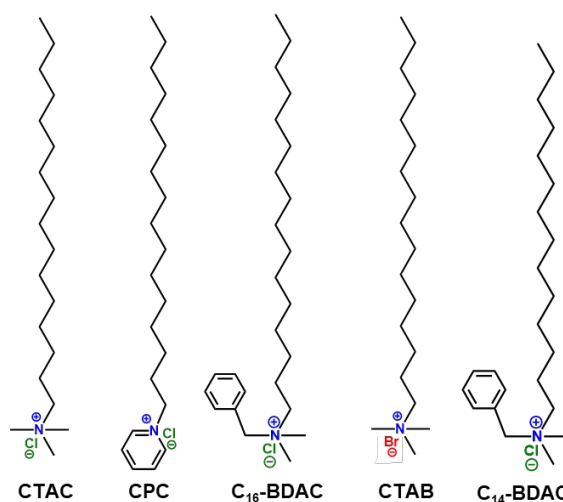


Scheme 1. A schematic representation of the chemical structure of the different surfactants used in the present study.

Carrying out a systematic variation of surfactant structural parameters on the final Au NP morphology allows us to interpret the precise chemical interactions that lead to the observed morphological changes. Our findings provide a more wholistic picture on the role of the quaternary ammonium surfactants in seed-mediated growth of Au NPs that can be implemented to other metal NP systems as well which make use



of these surfactants. Furthermore, we realize that binary surfactants, where either $C_{16}PX$ or $C_{16}TAX$ ($X=Cl$) is present in excess over other chloride or bromide-based surfactants, yield better control over shape than using a single surfactant and the resultant Au NPs displayed more defined stellations. Overall, the structural parameters of the surfactants obtained from small angle X-ray scattering (SAXS) were consistent with the observations from scanning electron microscopy (SEM) and nuclear magnetic resonance (NMR) data collected for Au NPs synthesized with these surfactants, allowing us to arrive at our conclusions as dictated in Scheme 2, namely that 1) increasing the surfactant headgroup bulkiness leads to fewer stellations, 2) increasing the surfactant chain length increased the resulting particle size, and 3) changing the counter anion species affected the formation and sharpness of the NP stellation. Surprisingly though under seedless conditions when the binary surfactants were employed, only the bromide containing binary surfactant mixture resulted in the formation of stellated Au NPs while the chloride-only binary surfactant mixture continued to generate concave cube Au NPs.

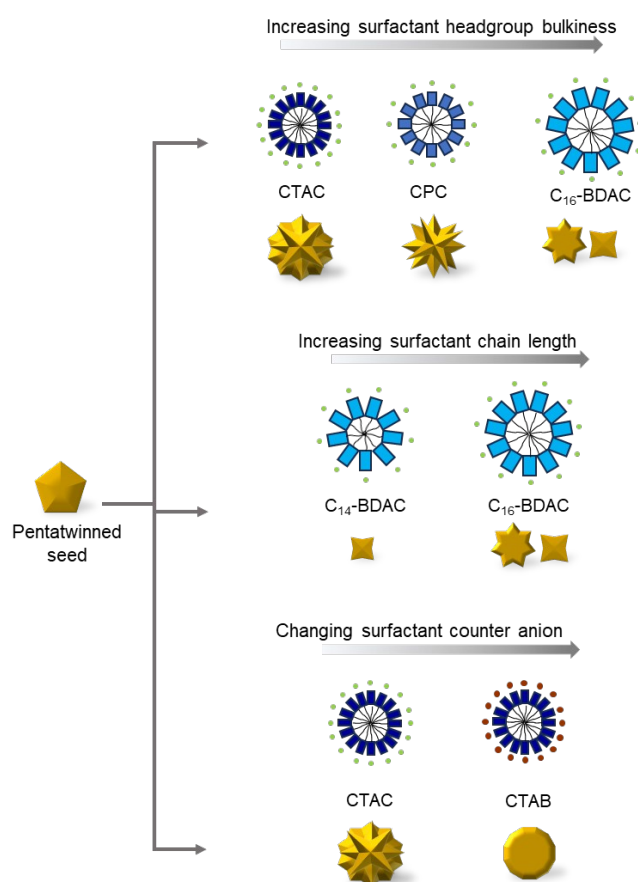

Scheme 2. Summary of variation of different surfactant structural parameters, headgroup, chain length, and counter-anion on the final Au NP morphology from a pentatwinned Au seed.

Materials and Methods

View Article Online

DOI: 10.1039/D5NA00754B

Chemicals. Silver (I) nitrate (>99.99%), gold (III) chloride trihydrate, tannic acid, cetyltrimethylammonium chloride, cetylpyridinium chloride, cetylpyridinium bromide, benzyldimethylhexadecylammonium chloride, benzyldimethyltetradecylammonium chloride, and sodium borohydride were purchased from Aldrich. Sodium hydroxide (ACS-grade) was bought from Macron and cetyltrimethylammonium bromide was purchased from Bioworld. Citric acid was purchased from J. T. Baker Inc. All chemicals were used as received without additional purification. All H₂O used to make solutions was UltraPure Type 1 Deionized Water (ChemWorld). All glassware was washed with aqua regia and dried under nitrogen prior to use. To prepare 5 mL of 200 mM surfactant solutions, respective amounts of the surfactants (CTAB, CPC, CPB, C_{16} -BDAC, C_{14} -BDAC) were weighed out and dissolved completely in ultrapure DI water to obtain a clear solution which was stored in a 100 mL glass reagent bottle. A 5 mL 200 mM CTAC solution was prepared using CTAC solution (25 wt.% in H₂O) purchased from Sigma-Aldrich. All surfactant and tannic acid solutions used were prepared immediately prior to the syntheses, while gold and silver precursor solutions were prepared and stored in amber glass reagent bottles for approximately one week.

Synthesis of pentatwinned Au NPs used as seeds. The synthesis of Au pentatwinned NPs used in the present study was carried out by following a previously reported synthetic protocol.⁶⁶ Au pentatwinned NPs generated in high yield was subjected to overgrowth without further purification. Briefly, to an aqueous 50 mM CTAC solution, 10 mL 0.25 mM HAuCl₄ and 5 mM citric acid was added, followed by the addition of 0.25 mL 25 mM freshly prepared NaBH₄ solution under vigorous stirring at room temperature which turned the solution from light yellow to brown. The round-bottom flask was closed after 2 minutes and the solution was heated at 80 °C for 90 minutes under gentle stirring. To prevent explosion of the flask, a needle was inserted through a Teflon tape sealing to prevent positive pressure build-up. The colour of the solution changed from brown to red and the seed solution was removed from heat and stored in a glass vial at room temperature for months without disintegration.

Synthesis of stellated Au NPs using a single surfactant. To synthesize Au NPs, we developed a novel synthetic route. A growth solution was prepared by adding 702 μ L UltraPure DI water, 1 mL, 200 mM CTAC (CPC, C_{16} -BDAC, C_{14} -BDAC, CTAB or CPB), 250 μ L 4 mM HAuCl₄, 10 μ L 4 mM AgNO₃, and 20 μ L 100 mM NaOH. This was followed by the addition of 10 μ L 100 mM tannic acid which resulted in a color change of the solution from yellow to pale tan. Following the color change, 8 μ L of the pentatwinned seed solution was introduced to the growth solutions to initiate the reaction and left undisturbed overnight. The resultant Au NPs were centrifuged three times at 9900 \times g RCF for 5 minutes where the supernatant was discarded while the pellet of the particles was redispersed in ultrapure DI water. After three rounds of centrifugation, the volume was reduced 10 times from the starting Au NP solution to maintain a final volume of 200 μ L of purified Au NPs redispersed in ultrapure DI



water. This was used for further characterization which was performed within days of the syntheses. The particles were confirmed to be stable for up to 3 months.

Synthesis of stellated Au NPs using a binary surfactant mixture. A novel synthetic protocol was devised which is outlined below. To synthesize Au NPs, a growth solution was prepared by adding 702 μL ultrapure DI water, 750 μL , 200 mM CTAC or CPC and 250 μL 200 mM CTAB or C_{16} -BDAC or C_{14} -BDAC, to make the volume up to 1 mL, 250 μL 4 mM HAuCl_4 , 10 μL 4 mM AgNO_3 , and 20 μL 100 mM NaOH. This was followed by the addition of 10 μL 100 mM tannic acid which resulted in a color change of the solution from yellow to pale tan. Following the color change, 8 μL of the pentatwinned seed solution was introduced to the growth solutions to initiate the reaction and left undisturbed overnight. The resultant Au NPs were centrifuged thrice at $9900 \times g$ RCF for 5 minutes for purification and to enable further characterization. For the seedless control condition, no seed solution was introduced to the growth solution.

Scanning Electron Microscopy (SEM). All SEM images were collected using the FEI Apreo VolumeScope SEM. The samples for SEM imaging were prepared by dispersing the washed sample in DI water, so that the final volume was 200 μL . 10 μL of the respective sample dispersions were drop-cast on ultra-flat Si wafers and allowed to dry overnight in a desiccator. The size analysis on the Au NPs were carried out manually using ImageJ software on over 100 particles for each sample. The images were collected over 5 places on the Si wafer.

Small Angle X-Ray Scattering (SAXS). A Xenocs Xeuss 3.0 HR SAXS instrument was used to collect data using a Cu source. Identical concentration and volume of the surfactant used in the synthesis was maintained to prepare the solution for measurement. UltraPure water (18.2 M Ω) was added so that the resultant concentration of the surfactants used for synthesis was maintained (100 mM). The surfactant solutions were then placed in 1.5 mm quartz capillaries for measurement with a slit size of 0.35 x 0.7 mm. The scattering intensity of Au NPs being much higher than the surfactants, all measurements were carried out only on the surfactant solution to extract useful data. Raw CCD images containing 2D scattering patterns were reduced to 1D q -space patterns in XSACT software. The sample-to-detector distance was 370 mm and was calibrated using the pattern of a silver behenate calibrant. 2D patterns were azimuthally averaged to extract the 1D patterns.

Nuclear Magnetic Resonance (NMR) Spectroscopy. ^1H NMR spectra were obtained using a Bruker Advance Neo 500 MHz spectrometer with a Bruker iProbe probe. The number of scans was set to 256, with a delay time of 1.0 sec, and a line broadening of 0.30 Hz for the surfactants while the number of scans was increased to 1024 for the Au NPs while keeping all other parameters the same. Surfactant solutions were prepared in D_2O , maintaining a resultant concentration of 100 mM. Aqueous NP solutions were centrifuged (same centrifuge conditions used as for NP purification) and re-dispersed in UltraPure water three times prior to measurements to remove

any unreacted species. The Au NPs were resuspended in pure D_2O after washing.

DOI: 10.1039/D5NA00754B

Results and Discussions. The current study takes an extensive look at the structural parameter aspect of the quaternary ammonium halide-based surfactants which are commonly employed in aqueous seed-mediated synthesis of noble metals, especially Au NPs. A systematic approach is employed to understand individually how the steric, hydrophobicity, and electrostatic effect associated with the head-group, hydrocarbon chain length, and counter-anion respectively affects the final NP morphology (Scheme 1). To provide a comprehensive understanding, both seed-mediated synthesis employing a pentatwinned starting seed as well as a seedless approach have been employed.

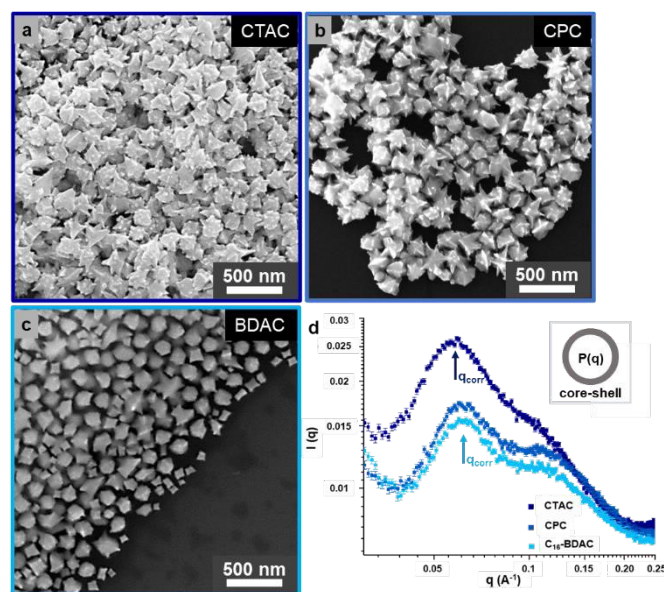


Figure 1. (a-c) SEM images of Au NPs synthesized using surfactants with increasing headgroup bulkiness show the formation of Au NPs with fewer stellations and increased shape polydispersity. (d) SAXS patterns of surfactants having the same chain length and counter anion but different headgroup, CTAC, CPC, BDAC indicate changing peak positions and scattering intensity. Inset d: Representative image of the core-shell micellar structure adopted by the surfactant.

Bulky headgroups result in Au NPs with fewer stellations and more shape polydispersity

The effect of the surfactant sterics on NP morphology was undertaken by employing three chloride-based surfactants with identical chain length but differing headgroup bulkiness, namely CTAC, CPC, and BDAC in an increasing order of bulkiness respectively. These cationic surfactants differing only in their headgroup were probed using SAXS to enable us to interpret the effect of the surfactant headgroup on the intermicellar and intramicellar interactions (Figure 1d). Previous studies have shown the formation of micelles for such cationic surfactants, while vesicle formation was attributed to the presence mixed cationic anionic surfactants.^{29, 71-73} Figure 1d exhibits the scattering cross-section of the three chloride-based surfactants with identical chain lengths and counter anion at the same



resultant concentration (0.1 M). The scattering cross-section for all three cationic surfactants are characterized by a peak and a shoulder which indicates the formation of a core-shell form factor that arises as the chloride counterion condenses inside the polar shell of the micelle. The inset in Figure 1d is a representative image of the core-shell micellar structure adopted by the surfactant, with a hydrocarbon micellar core and a polar shell. The contrast difference between the micellar core and the solvent and between the polar shell and the solvent vary according to the electron density of the atoms involved. This gives rise to a form factor peak which results in a double peak, typically associated with core-shell form factors in SAXS.⁷⁴ The intermicellar repulsion arising for the three cationic micelles give rise to strong structure factor contributions resulting in a correlation peak (q_{corr}). The mean intermicellar distance, d_{im} , thus can be derived from the q_{corr} peak as $d_{im} = 2\pi/q_{corr}$. The q_{corr} values obtained from the SAXS data were found to follow the order CTAC < CPC < BDAC (Table S1), leading to mean intermicellar distance values which follow a reverse order (CTAC > CPC > BDAC). Similar values reported previously for the said surfactants at a concentration of 0.1 M lend credibility to our findings.^{70, 74, 75} Thus, the higher d_{im} values associated with CTAC indicate that it forms fewer micelles (indicated by low number density N_d) with more molecules per micelles (represented by higher aggregation number N_{agg}) than CPC which in turn forms fewer and larger micelles when compared to BDAC as the same total number of molecules are present in the solution (0.1M). Moreover, the low scattering cross-section observed for CPC and BDAC can be attributed to the electron resonance within the benzene headgroup. The second peak observed in the SAXS curve at higher q values arises from the scattering of the condensed chloride counter anions arranged around the micelles as the polar shell.^{70, 74, 75}

The corresponding electron microscopy images (Figure 1a-c) of Au NPs synthesized using these surfactants show that increasing the bulkiness of the headgroup not only resulted in fewer branches but also narrower arms. BDAC with the bulkiest headgroup among the three not only resulted in less branched Au NPs but also a sizable proportion of concave cube Au NPs. Additionally, a minor reduction in dimension of the Au NPs was observed with increase in the headgroup size. Since these surfactants form a bilayer on the Au NP surface with the polar headgroup binding to the metal surface, the bulkiness of the headgroup will dictate the packing density of the surfactants and hence the permeability of the metal atoms being reduced.²⁷ Thus, CTAC with the least bulky headgroup among the three will have the most closely packed surfactant layers on the Au surface while BDAC will have the most loosely packed surfactant bilayer as determined from our SAXS data. This will enable more diffusion of the Au atoms to the Au surface resulting in Au NPs with bigger core and fewer arms when BDAC was employed. Since diffusion will be restricted in closely packed surfactant bilayer, deposition will dominate giving rise to wider arms for Au NPs synthesized using CTAC.

Surfactant chain length affects the dimension of Au NPs

The correlation of the surfactant chain length to the Au NP morphology was investigated by using chloride based surfactants with identical polar headgroups but different chain lengths (C_{16} -BDAC vs C_{14} -BDAC). The SAXS data obtained for C_{16} -BDAC and C_{14} -BDAC show that they are strongly influenced by the surfactant chain length (Figure S1a). The chain length and therefore the volume of the hydrophobic tail of the surfactants is known to determine the core radius of the micelle. A smaller core radius will arise from the C_{14} -BDAC in comparison to the C_{16} -BDAC.^{26, 76} Thus, the size of the micelle can be varied simply by changing the length of the hydrophobic tail of the surfactants as observed from the corresponding SAXS curves where the correlation peak q_{corr} for the shorter chain BDAC surfactant appears at higher q values indicating a decrease in the average intermicellar distance d_{im} for C_{14} -BDAC (Table S2).

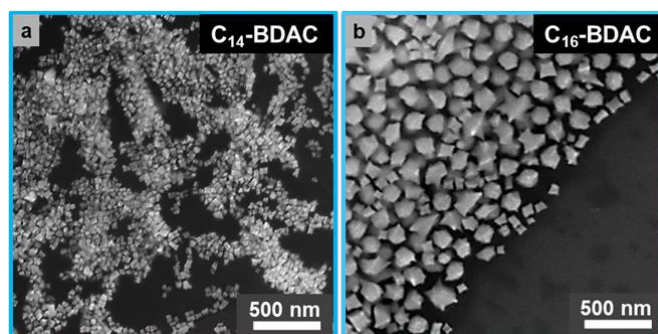


Figure 2. (a-b) SEM images of Au NPs synthesized using surfactants with increasing hydrocarbon chain length show the formation of Au NPs with increasing dimension.

To accommodate the extra hydrocarbon present in C_{16} -BDAC over C_{14} -BDAC in the micellar core, not only do we observe the formation of a larger micelle but also the formation of an ellipsoidal micelle instead of a spherical micelle. The width of the peak is correlated with the charge on the micelles.³⁰ We observe with increase in the hydrocarbon chain length, there is an increase in the concentration of the counter anions bound to the micellar shell, which enables the screening of headgroup repulsion, bringing the headgroups closer and reducing the charge on the micelles. These observations resonate with previous findings where smaller micelles with more fractional charges on the shell was observed for shorter chain length cationic surfactants than their longer chain counterparts.^{31, 77} Previous studies on Au nanorods (NRs) carried out by systematic variation of surfactant chain length (C_{10} - C_{16}) showed that increasing the hydrocarbon chain length resulted in the formation of longer NRs irrespective of whether a seed-mediated method or a photochemical method was employed.^{51, 52} On the other hand, a reverse correlation between chain length of ligand to NP size was realized in hot injection methods commonly employed to synthesize semiconductor NPs.⁷⁸ In the present study, our observations are in line to those observed for seed-mediated Au NRs. C_{14} -BDAC gave rise to concave cube Au NPs with average length 44 ± 5 nm and average width 34 ± 5 nm, which is almost half when compared against the concave cube



Au NPs generated using C₁₆-BDAC (average length 86±14 nm and average width 61±12 nm) (Figure 2). The longer chain surfactant resulted in a mix of concave cube Au NPs and stellated Au NPs, while a better shape uniformity was achieved with the shorter chain surfactant. This observation can be rationalized by considering that increasing the surfactant chain length results in the formation of ellipsoidal micelle instead of a spherical micelle, allowing greater diffusion of the reduced Au atoms at the micellar ends for C₁₆-BDAC surfactant. This gives rise to larger Au NPs. The anisotropic micellar morphology was also responsible for the poor shape uniformity arising from C₁₆-BDAC. For the C₁₄-BDAC we observe an isotropic micelle due to its spherical shape. This results in smaller and more uniform concave cube Au NPs.

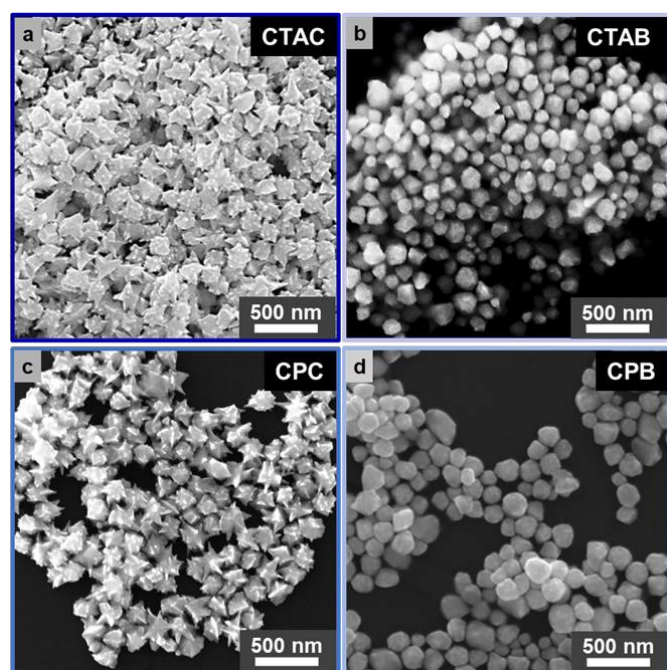


Figure 3. (a-b) and (c-d) SEM images of Au NPs synthesized using different surfactants differing only in the counter-anion associated with the surfactant show that the final NP morphology is dramatically affected by changing the counter-anion.

Surfactant counter-anion affects the morphology of the Au NPs

Comparing the influence of the surfactant counterion on SAXS patterns of CTAC and CTAB we find that the effect on the intermicellar interactions is more prominent than the effect of the headgroup chemical structure. Given that the surfactants have identical structural parameters except for the halide counter anion, we observe that the SAXS patterns are significantly different from one another as corroborated from literature reports.^{32, 70, 74} The intermicellar distance of CTAB determined from q_{corr} was found to be longer than CTAC (Table S3). This is in line with previous reports which points towards the formation of fewer but larger micelles for CTAB than CTAC at the same concentration (0.1 M).^{32, 70, 74} The increase in micellar size is also indicative of more ellipsoidal shaped CTAB micelles when compared to CTAC. This difference arises due to the condensation behaviour of the counter anion. The chloride

counter anions generate stronger intermicellar repulsion that results in an enhanced structure factor for CTAC. The bromide counter anions on the other hand are bound more efficiently providing better electrostatic screening and hence weaker intermicellar repulsion. This determination is further compounded by the lower electronic density of chloride than bromide, as scattering varies as the square of the electron density of the atom, hence weaker scattering contrast. Taken together, these factors contribute to a higher scattering cross-section magnitude for CTAC micelles as is observed in Figure S1b. The prominent shoulder in the SAXS curve associated with CTAB is indicative of a higher concentration of counter anions having higher contrast condensed within the polar shell, thereby enhancing the form factor contribution of the core-shell. Thus, it can be inferred that the presence of bromide ions forms a more compact monolayer around the CTA⁺ micelle than the layer formed in the presence of chloride ions. This will have implications on atom deposition and diffusion as will be subsequently discussed.

The influence of surfactant counter-anion has been investigated previously in the context of seed-mediated synthesis of Au NPs where single crystalline NPs have been employed as starting seeds. We explore the effect of the halide counter-ion in the overgrowth of the pentatwinned Au seeds by employing two sets of C₁₆-based surfactants, C₁₆TAX and C₁₆PX (X= Cl/Br). In both cases we observe that the chloride-based surfactants result in stellated structures whereas their bromide counterparts are unable to give rise to any defined Au NP morphology (Figure 3). As demonstrated in previous studies, changing the halide counter anion associated with the surfactant changes the reduction potential of the metal precursor and hence the rate of Au⁺ reduction.^{5, 24, 25, 58} Thus, in the presence of chloride-based surfactants, the Au-chloride complex exists which is easier to reduce than the Au-bromide complex formed in the presence of the bromide-based surfactants.^{5, 58} In addition to this, the solubilities of the Au-halide complexes also decrease with increasing size of the corresponding halide, changing the effective Au⁺ concentration in solution and hence the availability of Au⁺ for reduction.^{5, 58} This is further compounded by the adsorbate binding strength of the halide to the Au NP surface by modifying the amount of surface area available for catalyzing the reduction of Au⁺ to Au⁰.^{5, 58} With binding strength of Cl⁻ < Br⁻, the corresponding desorption of the halide from the NP surface becomes increasingly difficult, lowering the Au surface area to facilitate the reduction of Au⁺.^{5, 58} These parameters will affect the



reduction rate of the precursor and thus the NP growth kinetics. Therefore, in the presence of the chloride-based surfactant the rate of Au atom generation being faster than that in the presence of the bromide-based surfactant, the rate of atom deposition (R_{dep}) exceeds the rate of atom surface diffusion (R_{diff}).^{79–81} Consequently, the atom deposition takes place at the intrinsic strains present in the pentatwinned Au seeds which are unstable and associated with high energy along with the unprotected corners, to minimize the overall energy associated with the growing NP. Since $R_{\text{dep}} \gg R_{\text{diff}}$, the position of the newly deposited atoms remains unchanged, subsequently transforming the pentatwinned seed into a stellated Au NP. On the other hand, in presence of the bromide-based surfactants, a slower generation of the Au atoms allows for the migration of the newly deposited atoms to the edges and side faces of the pentatwinned seeds as $R_{\text{diff}} \gg R_{\text{dep}}$. Previous studies on the

surfactant organization on Au surfaces have shown that CTAC gives rise to patchy or discrete micelle formation while CTAB generates a compact bilayer formation around the NP surface.⁴⁵ The presence of patchy CTAC micelles enables multiple channels for rapid Au deposition to take place on the pentatwinned seeds resulting in the stellated Au NPs we observe. On the other hand, the CTAB bilayers on Au NPs are just as compact as their free micelles in water, and the rate of Au atom generation is also significantly lowered than in the presence of CTAC. Taken together, the above reasons account for the absence of any stellation and defined morphology observed for the Au NPs.

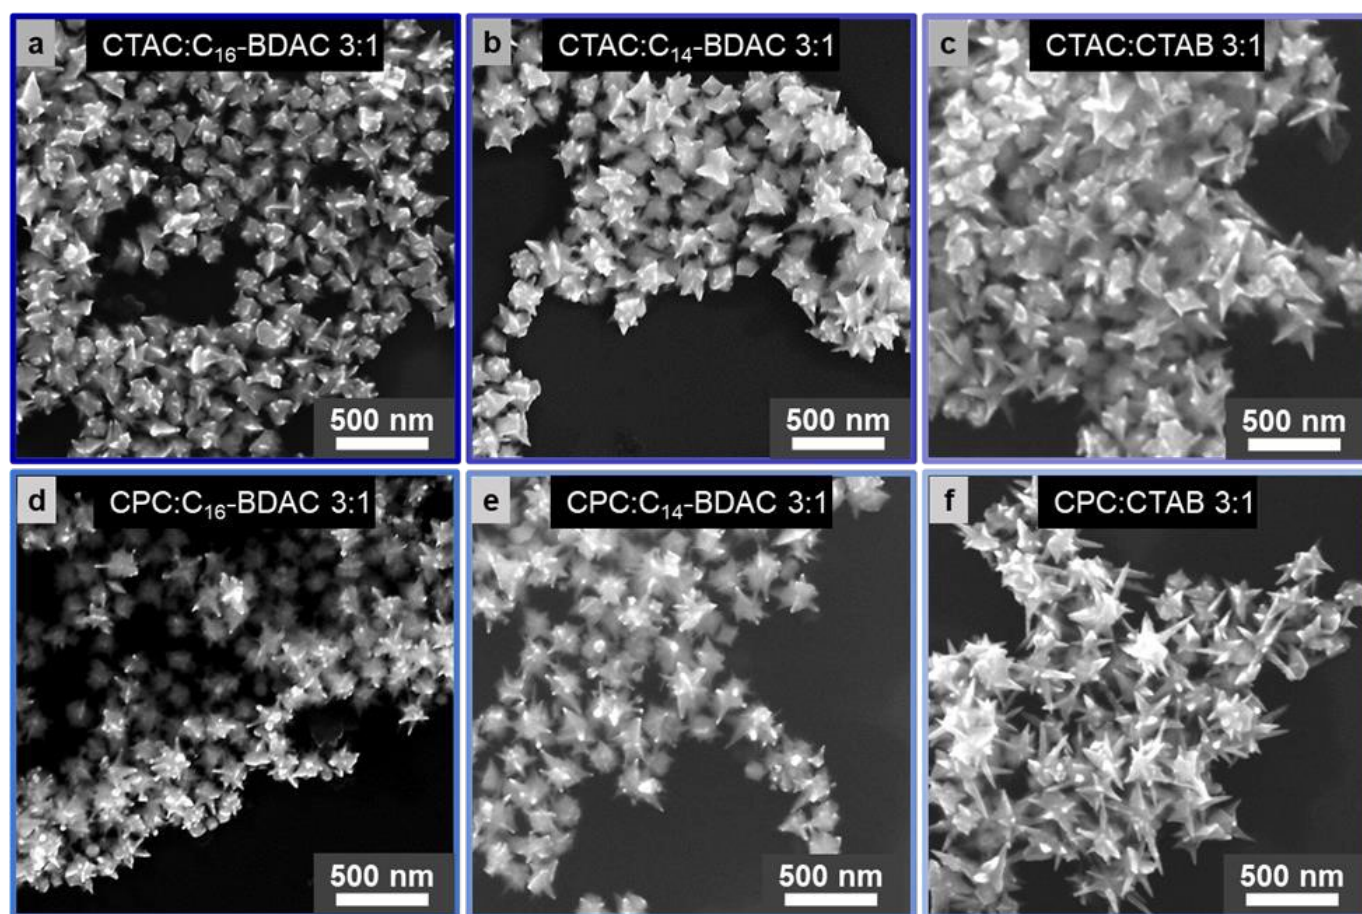


Figure 4. SEM images of stellated Au NPs synthesized using (a-c) CTAC-based binary surfactants mixture and (d-f) CPC-based binary surfactants showing a better control over morphology.

Binary surfactant mixture leads to better morphological control of Au NPs

To further investigate the dependence of the Au NP morphology on the structural parameters of the surfactant, we performed the synthesis of Au NPs using a mixture of surfactants employed in the current study. This involved combining a chloride-based surfactant (CTAC or CPC) in excess with other surfactant having a different headgroup or chain length (C_{16} -BDAC or C_{14} -BDAC)

or different counter anion (CTAB) while maintaining an overall constant surfactant concentration. Figure 4 indicates that the stellations on the Au NPs are more defined in the presence of the binary surfactant mixture. We find that the presence of bromide in the surfactant mixture not only resulted in a defined number of arms, but also larger Au NPs. The same conclusion holds for the CPC-dominated surfactant mixtures. The arrangement of mixed surfactants around NP surface is still



debatable with some attributing to the formation of alternating stripes of similar surfactant on the NP surface⁸², while others have categorized it to Janus, patchy or random.^{83, 84} While a quantitative picture of the mixed surfactant arrangement around the NP surface is improbable for us, nuclear magnetic resonance (NMR), a non-destructive technique can give an idea about the surface landscape of the resultant Au NPs.⁸⁵ Although NMR for larger particles present a complicated spectra with significant peak broadening^{86, 87} unlike what is observed in the present study, we cannot entirely rule out effects of ligand exchange in the solution or concentration-based effects. We used NMR to look at surfactants, obtaining reasonable data as have others, when one dimension of the particles is sufficiently small to allow for rotation of the ligand on the NP surface (in this case, the stellated tips, which are less than 25 nm in size). The ¹H NMR measurements carried out on the Au NPs exhibit peaks characteristic to both the surfactants used in the synthesis, thereby confirming that the usage of binary surfactants acts synergistically to improve the shape of the resultant Au NPs (Figures S2-S7).^{27, 50, 88-91} Additionally, the upfield shift of the proton peaks situated in the vicinity of the nitrogen head group indicates the interaction of the surfactant molecules to the Au NP surface through their headgroups. The SAXS data on the other hand collected for the mixed micelles exhibit the correlation peak which do not conform to the q_{corr} values of the individual surfactants (Figure S8). As can be expected, the peak positions are similar to the dominating surfactant present in the solution (Table S4 and S5). Unfortunately, other than endorsing the fact that the binary surfactants give rise to a mixed micelle instead of individual micelles, the SAXS data is unable to provide more information on their arrangement.²⁸ Our SAXS data, while suggesting that the binary surfactant mixtures are homogeneously bound, we cannot rule out entirely the possibility that there may be local clustering.⁸² We can only determine the intermicellar and intramicellar distances from the SAXS data, neither of which provides quantitative evidence for the mixed surfactant arrangement in these micelles. The presence of an additive/co-surfactant has been confirmed previously to modify the micellar arrangement around Au NPs.^{6, 46-50} We postulate that this modification can account for why more defined stellations are observed in presence of the binary surfactants, especially when CTAB is present. When CTAB is present in the binary surfactant mixture, its concentration is not enough to enforce a compact bilayer around the Au NP surface. Neither is the Au NP surface surrounded with the patchy micellar globules of the chloride-based surfactant only. The presence of the binary surfactant changes the individual micellar arrangement around the Au NPs. This results in narrower channels for Au atom deposition giving rise to Au NPs with the most well-defined stellations (Figure 4c, f). Surprisingly, when the same reactions were carried out in the absence of any seeds, it was found that only in the presence of bromide-based surfactants did the formation of the stellated Au NPs take place (Figure S9). The chloride-based binary surfactant mixtures irrespective of the surfactant headgroup or chain length consistently resulted in the formation of the concave cube Au NPs. In our earlier work we

have shown that decahedra Au NPs with five-fold twinning and bound by {111} planes gave rise to stellated NPs in presence of a binary containing bromide, while giving rise to concave cube in presence of chloride-based surfactant.⁹² Additionally, in the seminal work by Mirkin and co-workers, Au concave cube NPs were generated when chloride-based surfactants were used both for the seed synthesis as well as the overgrowth.⁹³ Thus, it is not entirely surprising that concave cube Au NPs are formed in the chloride-based binary surfactant mixture. We postulate that when bromide is present in the surfactant mixture, the initial seeds formed are bound primarily by {100} planes and $R_{diff} < R_{dep}$ results in the deposition of the newly generated atoms at the corners resulting in stellated Au NPs that are observed.

Conclusions

In this work we have meticulously examined the structural parameters, headgroup, hydrocarbon chain length, and counter-anion, associated with quaternary ammonium halide-based surfactants commonly employed in aqueous seed-mediated growth method of Au NPs. This was accomplished using SEM, NMR in conjunction with SAXS techniques which together provide thorough structural probes. Subjecting the pentatwinned seeds to overgrowth in presence of surfactants whose parameters were systematically varied allowed us to observe the dominance of each individual parameter on the resultant Au NPs. We found that a less bulky headgroup allows for a closer packing of the surfactant bilayers enabling a tighter control over the shape yield; while the hydrocarbon chain length regulates the size of the resultant Au NPs. On the other hand, the counter-anion associated with the surfactant controls the shape of the final Au NPs. To the best of our knowledge this is the first instance of such a detailed investigation being undertaken on the structural parameters of the quaternary ammonium cationic surfactants in seed-mediated synthesis. We further realize that rationally tailored binary surfactant mixtures enable better morphological control over the resultant Au NPs, both with and without the presence of seeds. We anticipate that these findings will not only advance synthetic methodology pertaining to Au NPs but also open up the understanding for other systems which make use of such surfactants.

Author contributions

The project was conceptualized by D. Roy, who also synthesized all particles and performed microscopy, NMR, and SAXS measurements. The manuscript was written by D. Roy and L. M. Moreau. All authors have given approval to the final version of the manuscript.

Conflicts of interest

There are no conflicts to declare.

Data availability



Additional SEM images along with NMR, and SAXS data supporting this manuscript have been included as part of the Supplementary Information.

Acknowledgements

The NMR spectrometer equipment is supported by the M.J. Murdock Charitable Trust, Grant #SR-201912845, and private donors Don and Marianna Matteson. Funding for the SAXS instrument was provided by the M. J. Murdock Trust, Grant #SR-202016425. We acknowledge the NUCS Core Facility at Washington State University for the NMR and SAXS data collection. The authors acknowledge the Franceschi Microscopy & Imaging Center (FMIC) at WSU for the SEM data.

Notes

Abbreviations. NPs, nanoparticles; NR, nanorod; CTAB, cetyltrimethylammonium bromide; CTAC, cetyltrimethylammonium chloride; CPC, cetylpyridinium chloride; BDAC, benzylidimethylhexadecylammonium chloride; C₁₄-BDAC, benzylidimethyltetradecylammonium chloride; CMC, critical micellar concentration; SEM, scanning electron microscopy; SAXS, small angle X-ray scattering; NMR, nuclear magnetic resonance.

References

- N. D. Burrows, A. M. Vartanian, N. S. Abadeer, E. M. Grzincic, L. M. Jacob, W. Lin, J. Li, J. M. Dennison, J. G. Hinman and C. J. Murphy, *J. Phys. Chem. Lett.*, 2016, **7**, 632-641.
- Y. Xia, K. D. Gilroy, H. C. Peng and X. Xia, *Angew. Chem. Int. Ed.*, 2017, **56**, 60-95.
- B. Nikoobakht and M. A. El-Sayed, *Chem. Mater.*, 2003, **15**, 1957-1962.
- Y. Xia, Y. Xiong, B. Lim and S. E. Skrabalak, *Angew. Chem. Int. Ed.*, 2009, **48**, 60-103.
- M. L. Personick and C. A. Mirkin, *J. Am. Chem. Soc.*, 2013, **135**, 18238-18247.
- M. S. Bakshi, *Cryst. Growth Des.*, 2016, **16**, 1104-1133.
- T. Song, F. Gao, S. Guo, Y. Zhang, S. Li, H. You and Y. Du, *Nanoscale*, 2021, **13**, 3895-3910.
- J. Mosquera, D. Wang, S. Bals and L. M. Liz-Marzán, *Acc. Chem. Res.*, 2023, **56**, 1204-1212.
- J. Xiao and L. Qi, *Nanoscale*, 2011, **3**, 1383-1396.
- R. Xiao, J. Jia, R. Wang, Y. Feng and H. Chen, *Acc. Chem. Res.*, 2023, **56**, 1539-1552.
- T. H. Yang, Y. Shi, A. Janssen and Y. Xia, *Angew. Chem. Int. Ed.*, 2020, **59**, 15378-15401.
- R. M. Crooks, M. Zhao, L. Sun, V. Chechik and L. K. Yeung, *Acc. Chem. Res.*, 2001, **34**, 181-190.
- Y. Shi, Z. Lyu, Z. Cao, M. Xie and Y. Xia, *Angew. Chem. Int. Ed.*, 2020, **59**, 19129-19135.
- G. Collins, F. Davitt, C. O'Dwyer and J. D. Holmes, *ACS Appl. Nano Mater.*, 2018, **1**, 7129-7138.
- H. Pu, H. Dai, T. Zhang, K. Dong, Y. Wang and Y. Deng, *Curr. Opin. Electrochem.*, 2022, **32**, 100927.
- L. Wei, H. Li, J. Chen, Z. Yuan, Q. Huang, X. Liao, G. Henkelman and Y. Chen, *ACS Catal.*, 2019, **10**, 1444-1453.
- X. Kong, J. Zhu, Z. Xu and Z. Geng, *Angew. Chem. Int. Ed.*, 2025, **64**, e202417562.
- J. Newton, J. Preece, N. Rees and S. Horswell, *Phys. Chem. Chem. Phys.*, 2014, **16**, 11435-11446.
- L. Wang, X. Jiang, Y. Ji, R. Bai, Y. Zhao, X. Wu and C. Chen, *Nanoscale*, 2013, **5**, 8384-8391.
- M. Bhamidipati and L. Fabris, *Bioconjug. Chem.*, 2017, **28**, 449-460.
- T.-L. Hwang, C. T. Sung, I. A. Aljuffali, Y.-T. Chang and J.-Y. Fang, *Colloids Surf. B: Biointerfaces*, 2014, **114**, 334-341.
- S. K. Meena and M. Sulpizi, *Langmuir*, 2013, **29**, 14954-14961.
- J. S. DuChene, W. Niu, J. M. Abendroth, Q. Sun, W. Zhao, F. Huo and W. D. Wei, *Chem. Mater.*, 2013, **25**, 1392-1399.
- S. E. Lohse, N. D. Burrows, L. Scarabelli, L. M. Liz-Marzán and C. J. Murphy, *Chem. Mater.*, 2014, **26**, 34-43.
- S. K. Meena, S. Celiksoy, P. Schäfer, A. Henkel, C. Sönnichsen and M. Sulpizi, *Phys. Chem. Chem. Phys.*, 2016, **18**, 13246-13254.
- C. Tanford, *J. Phys. Chem.*, 1972, **76**, 3020-3024.
- J. N. Israelachvili, D. J. Mitchell and B. W. Ninham, *J. Chem. Soc., Faraday Trans. 2*, 1976, **72**, 1525-1568.
- H. Pils, H. Hoffmann, S. Hofmann, J. Kalus, A. Kencono, P. Lindner and W. Ulbricht, *J. Phys. Chem.*, 1993, **97**, 2745-2754.
- R. Salkar, D. Mukesh, S. Samant and C. Manohar, *Langmuir*, 1998, **14**, 3778-3782.
- V. Aswal and P. Goyal, *Phys. Rev. E*, 2000, **61**, 2947.
- V. Aswal, P. Goyal, S. De, S. Bhattacharya, H. Amenitsch and S. Bernstorff, *Chem. Phys. Lett.*, 2000, **329**, 336-340.
- V. Aswal, P. Goyal, H. Amenitsch and S. Bernstorff, *Pramana*, 2004, **63**, 333-338.
- R. Nagarajan, *Langmuir*, 2002, **18**, 31-38.
- P. Llobart, M. A. Palafox, L. G. MacDowell and E. G. Noya, *COLL SURF A COLLOID SURF A PHYSICO-CHEM ENG ASP*, 2019, **580**, 123730.
- P. A. Hassan and S. L. Gawali, *Langmuir*, 2018, **35**, 9635-9646.
- N. K. Raman, M. T. Anderson and C. J. Brinker, *Chem. Mater.*, 1996, **8**, 1682-1701.
- B. Nikoobakht and M. A. El-Sayed, *Langmuir*, 2001, **17**, 6368-6374.
- S. Seibt, H. Zhang, S. Mudie, S. Förster and P. Mulvaney, *J. Phys. Chem. C*, 2021, **125**, 19947-19960.
- M. J. Hore, X. Ye, J. Ford, Y. Gao, J. Fei, Q. Wu, S. J. Rowan, R. J. Composto, C. B. Murray and B. Hammouda, *Nano Lett.*, 2015, **15**, 5730-5738.
- B. T. Diroll, K. M. Weigandt, D. Jishkariani, M. Cargnello, R. J. Murphy, L. A. Hough, C. B. Murray and B. Donnio, *Nano Lett.*, 2015, **15**, 8008-8012.
- S. Lee, L. J. Anderson, C. M. Payne and J. H. Hafner, *Langmuir*, 2011, **27**, 14748-14756.
- S. Gomez-Grana, F. Hubert, F. Testard, A. Guerrero-Martínez, I. Grillo, L. M. Liz-Marzán and O. Spalla, *Langmuir*, 2012, **28**, 1453-1459.
- F. Barbero, O. H. Moriones, N. G. Bastús and V. Puentes, *Bioconjug. Chem.*, 2019, **30**, 2917-2930.
- B. E. Janicek, J. G. Hinman, J. J. Hinman, S. H. Bae, M. Wu, J. Turner, H.-H. Chang, E. Park, R. Lawless and K. S. Suslick, *Nano Lett.*, 2019, **19**, 6308-6314.
- T. Zech, T. Schmutzler, D. M. Noll, M.-S. Appavou and T. Unruh, *Langmuir*, 2022, **38**, 2227-2237.
- M. Bakshi and I. Kaur, *Colloid Polym. Sci.*, 2003, **281**, 10-18.
- M. S. Bakshi and I. Kaur, *Colloid Polym. Sci.*, 2003, **281**, 935-944.
- M. S. Bakshi, I. Kaur, R. Sood, J. Singh, K. Singh, S. Sachar, K. J. Singh and G. Kaur, *J. Colloid Interface Sci.*, 2004, **271**, 227-231.
- J. Pérez-Juste, L. M. Liz-Marzán, S. Carnie, D. Y. Chan and P. Mulvaney, *Adv. Funct. Mater.*, 2004, **14**, 571-579.
- X. Ye, L. Jin, H. Caglayan, J. Chen, G. Xing, C. Zheng, V. Doan-Nguyen, Y. Kang, N. Engheta and C. R. Kagan, *ACS Nano*, 2012, **6**, 2804-2817.
- A. Kameo, A. Suzuki, K. Torigoe and K. Esumi, *J. Colloid Interface Sci.*, 2001, **241**, 289-292.
- J. Gao, C. M. Bender and C. J. Murphy, *Langmuir*, 2003, **19**, 9065-9070.
- D. Huang, Y. Qi, X. Bai, L. Shi, H. Jia, D. Zhang and L. Zheng, *ACS Appl. Mater. Interfaces*, 2012, **4**, 4665-4671.
- M. Tsuji, K. Matsumoto, T. Tsuji and H. Kawazumi, *Mater. Lett.*, 2005, **59**, 3856-3860.
- X. Kou, S. Zhang, C.-K. Tsung, M. H. Yeung, Q. Shi, G. D. Stucky, L. Sun, J. Wang and C. Yan, *J. Phys. Chem. B*, 2006, **110**, 16377-16383.
- X. Kou, S. Zhang, C. K. Tsung, Z. Yang, M. H. Yeung, G. D. Stucky, L. Sun, J. Wang and C. Yan, *Chem. Eur. J.*, 2007, **13**, 2929-2936.
- Y. Liu, D. Liu, T. Li and Y. Liang, *ACS Appl. Nano Mater.*, 2023, **6**, 21312-21321.
- M. R. Langille, M. L. Personick, J. Zhang and C. A. Mirkin, *J. Am. Chem. Soc.*, 2012, **134**, 14542-14554.
- H. Kawasaki, K. Nishimura and R. Arakawa, *J. Phys. Chem. C*, 2007, **111**, 2683-2690.
- Y. Hu, L. Wang, A. Song and J. Hao, *Langmuir*, 2018, **34**, 6138-6146.
- M. Grzelczak, A. Sánchez-Iglesias, B. Rodríguez-González, R. Alvarez-Puebla, J. Pérez-Juste and L. M. Liz-Marzán, *Adv. Funct. Mater.*, 2008, **18**, 3780-3786.
- M. Spirin, S. Brichkin, E. Yushkov and V. Razumov, *High Energy Chem.*, 2020, **54**, 308-315.
- M. Spirin, S. Brichkin, A. Lizunova and V. J. C. J. Razumov, *Colloid J.*, 2022, **84**, 100-108.
- O. Dement'eva, V. Matur, A. Zaikin, N. Salavatov, M. Staltsov and V. J. C. J. Rudoy, *Colloid J.*, 2022, **84**, 689-695.
- H.-L. Wu, C.-H. Chen and M. H. Huang, *Chem. Mater.*, 2009, **21**, 110-114.
- A. Sánchez-Iglesias, N. Winckelmans, T. Altantzis, S. Bals, M. Grzelczak and L. M. Liz-Marzán, *J. Am. Chem. Soc.*, 2017, **139**, 107-110.
- T. Sau and C. J. Murphy, *Philos. Mag.*, 2007, **87**, 2143-2158.
- Y. Nidome, Y. Nakamura, K. Honda, Y. Akiyama, K. Nishioka, H. Kawasaki and N. Nakashima, *Chem. Commun.*, 2009, 1754-1756.
- N. Almora-Barrios, G. Novell-Leruth, P. Whiting, L. M. Liz-Marzán and N. Lopez, *Nano Lett.*, 2014, **14**, 871-875.



ARTICLE

Journal Name

70. V. Lutz-Bueno, R. Pasquino, M. Liebi, J. Kohlbrecher and P. Fischer, *Langmuir*, 2016, **32**, 4239-4250.
71. E. W. Kaler, K. L. Herrington, A. K. Murthy and J. A. Zasadzinski, *J. Phys. Chem.*, 1992, **96**, 6698-6707.
72. C.-Y. Leung, L. C. Palmer, B. F. Qiao, S. Kewalramani, R. Sknepnek, C. J. Newcomb, M. A. Greenfield, G. Vernizzi, S. I. Stupp and M. J. Bedzyk, *ACS Nano*, 2012, **6**, 10901-10909.
73. G. Changrui, L. Honghao, L. Yue, K. Sumit and O. de la Cruz Monica, *J. Phys. Chem. B*, 2017.
74. V. Lutz-Bueno, M. Liebi, J. Kohlbrecher and P. Fischer, *Langmuir*, 2017, **33**, 2617-2627.
75. Y. Fan and Y. Wang, *Curr. Opin. Colloid Interface Sci.*, 2019, **42**, 1-16.
76. V. Aswal and P. Goyal, *Chem. Phys. Lett.*, 2002, **364**, 44-50.
77. S. Berr, *J. Phys. Chem.*, 1987, **91**, 4760-4765.
78. A. Sofie, S. Michael, J. Youngjin, C. Stefaan, L. Efrat and H. Zeger, *J. Am. Chem. Soc.*, 2015, **137**, 2495-2505.
79. Z. Lou, B. Huang, X. Qin, X. Zhang, H. Cheng, Y. Liu, S. Wang, J. Wang and Y. Dai, *Chem. Commun.*, 2012, **48**, 3488-3490.
80. H. Zhang, M. Jin and Y. Xia, *Angew. Chem. Int. Ed.*, 2012, **51**, 7656-7673.
81. A. Ruditskiy, H.-C. Peng and Y. Xia, *Annu. Rev. Chem. Biomol. Eng.*, 2016, **7**, 327-348.
82. C. Singh, Y. Hu, B. P. Khanal, E. R. Zubarev, F. Stellacci and S. C. Glotzer, *Nanoscale*, 2011, **3**, 3244-3250.
83. Z. Luo, D. Marson, Q. K. Ong, A. Loiudice, J. Kohlbrecher, A. Radulescu, A. Krause-Heuer, T. Darwish, S. Balog and R. Buonsanti, *Nat. Commun.*, 2018, **9**, 1343.
84. D. Roy, Y. Xu, R. Rajendra, L. Wu, P. Bai and N. Ballav, *J. Phys Chem. Lett.*, 2020, **11**, 3211-3217.
85. K. M. Greskovich, K. M. Powderly, M. M. Kincanon, N. B. Forney, C. A. Jalomo, A. Wo and C. J. Murphy, *Acc. Chem. Res.*, 2023, **56**, 1553-1564.
86. M. Wu, A. M. Vartanian, G. Chong, A. K. Pandiakumar, R. J. Hamers, R. Hernandez and C. J. Murphy, *J. Am. Chem. Soc.*, 2019, **141**, 4316-4327.
87. K. M. Hatzis, X. Wei, M. Kincanon, A. Wo, J. Gandrapu, O. Zeiri, R. Hernandez and C. J. Murphy, *Chem. Mater.*, 2025.
88. J. Ulmius, B. Lindman, G. Lindblom and T. Drakenberg, *J. Colloid Interface Sci.*, 1978, **65**, 88-97.
89. A. B. Mandal, L. Wang, K. Brown and R. E. Verrall, *J. Colloid Interface Sci.*, 1993, **161**, 292-298.
90. L. Okano, O. E. Seoud and T. Halstead, *Colloid Polym. Sci.*, 1997, **275**, 138-145.
91. K. Xu, H.-q. Ren, G.-m. Zeng, L.-l. Ding and J.-h. Huang, *Coll. Surf. A Colloid Surf A Physicochem Eng Asp*, 2010, **356**, 150-155.
92. D. Roy, H. C. Larson, B. M. Cossairt and L. M. Moreau, *Nanoscale Adv.*, 2025, **7**, 4412-4418.
93. J. Zhang, M. R. Langille, M. L. Personick, K. Zhang, S. Li and C. A. Mirkin, *J. Am. Chem. Soc.*, 2010, **132**, 14012-14014.

View Article Online
DOI: 10.1039/D5NA00754B



Data Availability Statement for
Elucidating the Role of Surfactant Structural
Parameters on Au Nanoparticle Morphology

Debashree Roy^a and Liane M. Moreau^{, a, b}*

^aDepartment of Chemistry, Washington State University, Pullman, WA 99164

^bDepartment of Chemistry, University of Wyoming, Laramie, WY 82071

AUTHOR INFORMATION

Corresponding Author

*Email – liane.moreau@wsu.edu

Email – lmoreau1@uwyo.edu



Data availability

View Article Online
DOI: 10.1039/D5NA00754B

Additional SEM images along with NMR and SAXS data supporting this manuscript have been included as part of the Supplementary Information. Other images and data are included in the main text. We have provided detailed protocols on how the data was collected. Our synthetic protocols are highly reproducible and all information pertaining to how to synthesize and purify them are included in the Methods section of the manuscript. If anyone would like to request the raw data collected from the instrumentation, we will share this upon request. We also encourage readers to reach out if they have trouble reproducing our results.

