

RESEARCH ARTICLE

View Article Online
View Journal | View Issue

Cite this: *Mater. Chem. Front.*,
2019, 3, 806

Antibacterial supramolecular polymers constructed *via* self-sorting: promoting antibacterial performance and controllable degradation†

Yuchong Yang,^a Hao Hu,^a Linghui Chen,^a Haotian Bai,^b Shu Wang,^b
Jiang-Fei Xu *^a and Xi Zhang ^a

An antibacterial supramolecular polymer is developed that exhibits enhanced antibacterial efficacy and controlled degradability. To this end, a water-soluble bifunctional monomer bearing two naphthalene moieties and a phenylbenzene moiety, as well as a small molecule with antibacterial activity were synthesized. The side-chain antibacterial supramolecular polymer was fabricated through self-sorting of the bifunctional monomer, the small-molecule antibacterial agent, and cucurbit[8]uril. It displayed enhanced antibacterial efficacy against ampicillin-resistant *E. coli* owing to the local enrichment effect. The controlled degradation of the antibacterial supramolecular polymer could well regulate its antibacterial performance from high to low activity. It is anticipated that this line of research may lead to novel antibacterial supramolecular materials for building degradable antibiotics with enhanced antibacterial efficacy to fight against drug-resistant bacteria.

Received 17th January 2019,
Accepted 4th March 2019

DOI: 10.1039/c9qm00028c

rsc.li/frontiers-materials

Introduction

Infections caused by drug-resistant bacteria are a severe threat to human health, because of the long-term abuse of antibiotics in medical treatments, the agricultural field *etc.*^{1–7} Prolonged antibiotic treatment can lead to an increase of bacterial drug resistance.⁸ To tackle this severe threat, supramolecular antibiotics have been employed to combat antibiotic resistance, benefiting from the dynamicity, degradability and reversibility of supramolecular interactions.^{9–27} To avoid long-term exposure to the active antibiotics, the antibacterial performance can be switched “on” and “off” by a supramolecular strategy, and the emergence of drug-resistant bacteria could be slowed down. However, to further inhibit the emergence of drug-resistant bacteria, there is a need not only to construct degradable antibiotics, but also to promote the antibacterial activity of such antibacterial materials.

We wondered if supramolecular polymers with controllable antibacterial efficacy could be fabricated. Supramolecular polymers refer to polymers in which monomers are connected with


each other *via* non-covalent interactions.^{28–56} By construction of supramolecular polymers, functional monomers can be linked together through reversible non-covalent interactions. Therefore, we assume that if small-molecule antibiotics could be linked together to form supramolecular polymers, the antibacterial efficacy could be significantly enhanced owing to the local enrichment effect. Besides, benefiting from the dynamicity and reversibility of supramolecular interactions, such antibacterial supramolecular polymers can be controllably degraded. Thus, enhanced antibacterial efficacy and degradability of antibacterial materials could be realized by fabricating antibacterial supramolecular polymers.

Herein, we attempted to construct a side-chain antibacterial supramolecular polymer *via* a self-sorting strategy. Self-sorting is a self-assembly process in which molecules are endowed with the ability to selectively and specifically form complexes with their own recognition units within a complex mixture.^{57–64} It has been reported that supramolecular polymers with controlled structure and molecular weight can be constructed through the self-sorting strategy.^{65,66} By employing this strategy, we designed a side-chain antibacterial supramolecular polymer, by which antibacterial agents could be grafted to the supramolecular polymer backbone as the side chains. Then antibacterial agents could be locally enriched for promoting antibacterial performance. Moreover, the backbone of the antibacterial supramolecular polymer could be controllably degraded, thus reducing the antibacterial activity in case of need. The architecture of the antibacterial

^a Key Lab of Organic Optoelectronics and Molecular Engineering, Department of Chemistry, Tsinghua University, Beijing 100084, China.
E-mail: xujf@mail.tsinghua.edu.cn

^b Key Laboratory of Organic Solids, Institute of Chemistry, Chinese Academy of Sciences, Beijing 100190, China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c9qm00028c

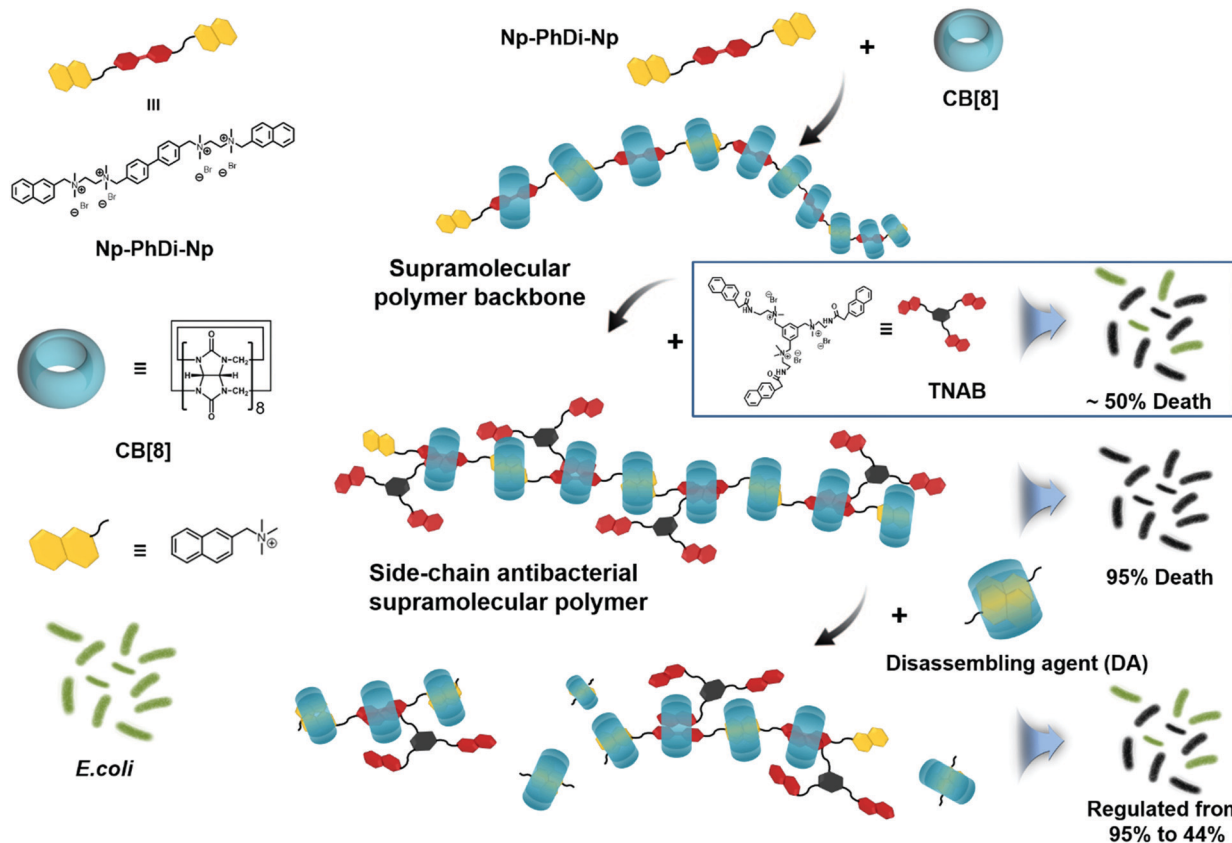

Scheme 1 Chemical structures of building blocks and schematic illustration of the fabrication of side-chain antibacterial supramolecular polymer.

supramolecular polymer consisted of two parts, the supramolecular polymer backbone and the side-chain antibacterial agents. As shown in Scheme 1, a bifunctional monomer (Np-PhDi-Np), containing two naphthalene (Np) moieties and a phenylbenzene (PhDi) moiety, was designed and synthesized to construct the supramolecular polymer backbone through the host-guest interaction of Np-PhDi-Np and cucurbit[8]uril (CB[8]).

A small molecule with antibacterial activity (TNAB) containing naphthalene acetamide (NpAM) moieties could be grafted to the supramolecular polymer backbone as side chains *via* self-sorting. The hydrophobic NpAM moieties of TNAB could insert into the membranes of bacteria for bacterial membranolysis. By locally enriching the TNAB on the supramolecular polymer backbone, the capacity for bacterial membranolysis may be remarkably increased. The degradation of the antibacterial supramolecular polymer could be realized by addition of a disassembling agent. Therefore, we may fabricate the antibacterial supramolecular polymer with tailor-made antibacterial efficacy and degradability.

Results and discussion

The fabrication of the supramolecular polymer backbone through the host-guest interaction of Np-PhDi-Np with CB[8] was demonstrated by isothermal titration calorimetry (ITC), ^1H NMR and diffusion-ordered NMR spectroscopy (DOSY). As shown in the ^1H NMR analysis in Fig. S1 (ESI †), when the molar

ratio of CB[8] to Np-PhDi-Np increased from 0 to 1.0, the peaks of Np moiety shifted up-field, while the peaks of PhDi moiety shifted down-field. These shifting peaks indicated that the CB[8] combined with Np moieties of Np-PhDi-Np primarily, acting as the driving force for supramolecular polymerization. When the molar ratio of CB[8] to Np-PhDi-Np increased from 1.0 to 2.0, the peaks of PhDi moiety shifted up-field, which indicated that the CB[8] combined with the PhDi moiety of Np-PhDi-Np subsequently. The two-step host-guest complexations were also indicated by ITC data, as shown in Fig. 1. The first abrupt change at a molar ratio of 1:1 could be ascribed to the complexation between CB[8] and Np moieties, and the second abrupt change at a molar ratio of 2:1 could be ascribed to the complexation between CB[8] and PhDi moiety. The two-step complexation may lead to the formation of the supramolecular polymer backbone.

Direct evidence for the formation of the supramolecular polymer backbone was demonstrated by DOSY. The diffusion coefficient of Np-PhDi-Np (0.25 mM) in water was $2.80 \times 10^{-10} \text{ m}^2 \text{ s}^{-1}$. After addition of 2 equivalents of CB[8], the diffusion coefficient was decreased to $1.10 \times 10^{-10} \text{ m}^2 \text{ s}^{-1}$, which indicated the formation of polymeric species. Taking the ^1H NMR data, ITC data and DOSY measurements into account, the supramolecular polymer backbone is formed on the basis of the host-guest complexations between Np-PhDi-Np and CB[8].

To fabricate a side-chain antibacterial supramolecular polymer, TNAB containing three NpAM moieties was designed as

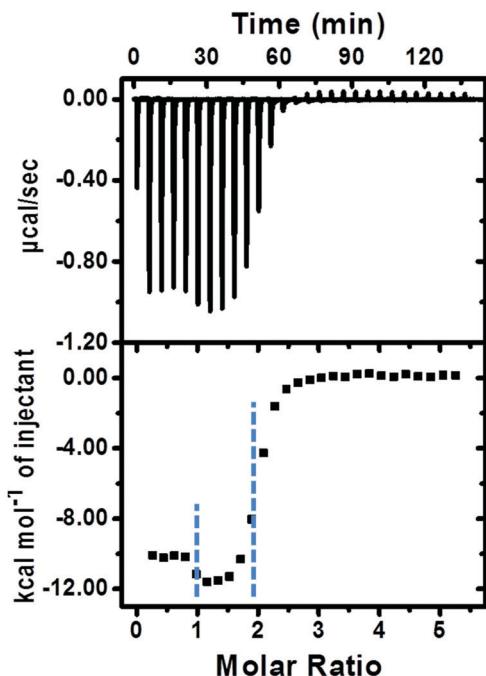


Fig. 1 ITC data (1× PBS buffer, pH = 7.0, 25.0 °C) of CB[8] (0.25 mM) titrated into Np-PhDi-Np (0.010 mM).

the side chains to graft to the supramolecular polymer backbone through self-sorting. The self-sorting among Np, NpAM, PhDi model molecules and CB[8] was studied by ¹H NMR, as demonstrated in Fig. 2. When Np, NpAM, PhDi model molecules and CB[8] were mixed at a ratio of 2:1:1:2, only the complexation between Np and CB[8] and the complexation of NpAM, PhDi and CB[8] were observed. The ITC data further demonstrated that Np could bind with CB[8] at a ratio of 2:1 with a binding constant of $2.25 \times 10^{12} \text{ M}^{-2}$. In addition, the NpAM moiety could insert into the supramolecular polymer backbone with a binding constant of $2.01 \times 10^5 \text{ M}^{-1}$, as shown

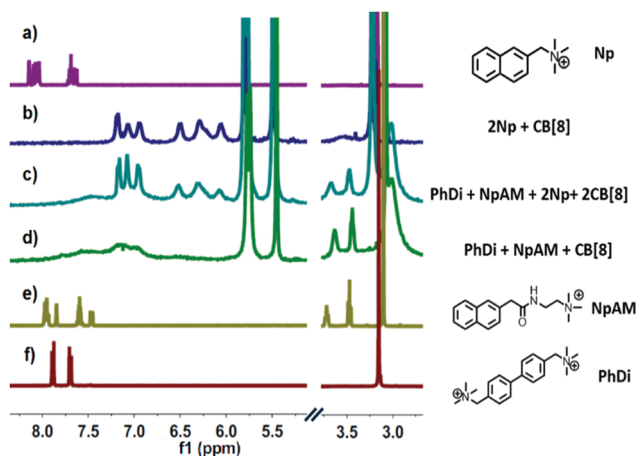


Fig. 2 Partial ¹H NMR spectra (400 MHz, D₂O, 25.0 °C) of (a) Np (2.0 mM); (b) 2Np-CB[8] (1.0 mM); (c) a mixture of Np (2.0 mM), NpAM (1.0 mM), PhDi (1.0 mM), and CB[8] (2.0 mM); (d) PhDi-NpAM-CB[8] (1.0 mM); (e) NpAM (1.0 mM); (f) PhDi (1.0 mM).

in Fig. S4 (ESI[†]). Based on the self-sorting of the model molecules, TNAB, containing three NpAM moieties, could insert into the supramolecular polymer as side chains for constructing the antibacterial supramolecular polymer.

The formation of the side-chain antibacterial supramolecular polymer was confirmed by analytical ultracentrifugation. As shown in Fig. S5a and b (ESI[†]), at a low concentration of 50 μM, the highest molecular weight of supramolecular polymer backbone was measured as $1.7 \times 10^4 \text{ Da}$, corresponding to a degree of polymerization (DP) of 5. After addition of TNAB, the molecular weight of the antibacterial supramolecular polymer was increased up to $2.1 \times 10^4 \text{ Da}$. The increased molecular weight indicated that 5 TNAB molecules were grafted to the supramolecular polymer backbone. Although there were three NpAM moieties on TNAB, the same DP of supramolecular backbone and antibacterial supramolecular polymer indicated that the crosslinking among the supramolecular polymer chains was negligible because of the low concentration. In addition, the DP of the antibacterial supramolecular polymer could be increased with increasing concentration of the building blocks. For example, the DP was measured to be 12 at a concentration of 0.50 mM, as shown in Fig. S5c (ESI[†]). Therefore, the side-chain antibacterial supramolecular polymer is successfully fabricated through self-sorting.

We have demonstrated successfully that antibacterial activity can be enhanced owing to the local enrichment of the antibacterial small molecules through the construction of the side-chain antibacterial supramolecular polymer. For comparison, antibacterial activity of the antibacterial supramolecular polymer, supramolecular polymer backbone and TNAB were investigated. As shown in Fig. 3, the supramolecular polymer backbone displayed almost no antibacterial activity, and the bacterial inhibition ratio of TNAB against ampicillin-resistant *E. coli* was

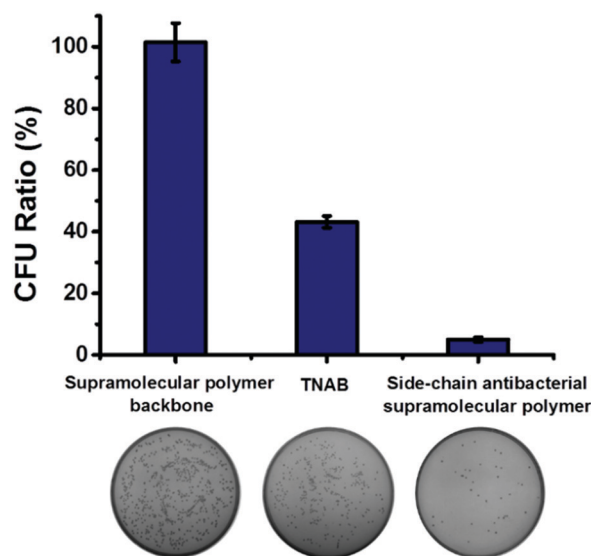


Fig. 3 The colony-forming unit (CFU) ratio of *E. coli* with antibacterial supramolecular polymer, supramolecular polymer backbone and TNAB. The concentrations of building blocks of supramolecular polymers and TNAB are 50 μM.

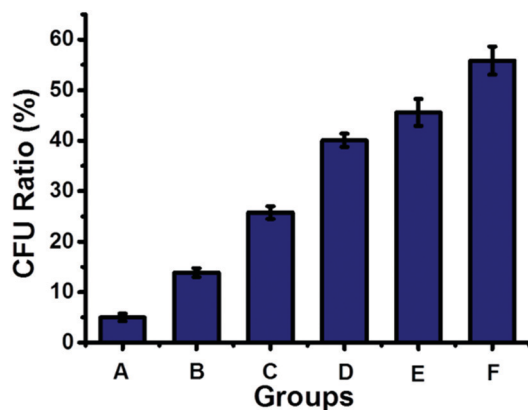


Fig. 4 The antibacterial activity of the antibacterial supramolecular polymer with different amounts of a disassembling agent, naphthalene derivatives (DA shown in Scheme 1). (A) 50 μ M antibacterial supramolecular polymer; (B) A + 10 μ M DA; (C) A + 20 μ M DA; (D) A + 30 μ M DA; (E) A + 40 μ M DA; (F) A + 50 μ M DA.

calculated as 57%. When TNAB was grafted to the supramolecular backbone for forming the antibacterial supramolecular polymer, the bacterial inhibition ratio was remarkably increased up to 95%. Therefore, the antibacterial activity can be promoted by fabrication of the antibacterial supramolecular polymer.

The dynamic nature of supramolecular interactions endowed the supramolecular polymer with degradability, which could be used to turn off the antibacterial activity of the antibacterial supramolecular polymer for avoiding long-term drug exposure. The antibacterial supramolecular polymer could be degraded by addition of a disassembling agent (DA), naphthalene derivatives, through competing with the host–guest interaction between Np and CB[8], as indicated by DOSY shown in Table S1 (ESI[†]). Then the antibacterial efficacy could be regulated by the controllable degradation of the antibacterial supramolecular polymer. As shown in Fig. 4, by gradual addition of the DA to the antibacterial supramolecular polymer, the bacterial inhibition ratio was gradually decreased from 95% to 44%. The controllable degradation of the antibacterial supramolecular polymer could diminish the enrichment of TNAB, leading to the decrease of antibacterial activity. Therefore, the antibacterial efficacy of the antibacterial supramolecular polymer can be well regulated from high to low activity.

ζ -Potential measurements and scanning electron microscopy (SEM) were employed to understand the interactions between the antibacterial supramolecular polymer and bacteria. Upon addition of the antibacterial supramolecular polymer, the surface charge of *E. coli* was altered from -48.0 mV to 19.9 mV (Table S2, ESI[†]), indicating that the positively charged antibacterial supramolecular polymer was adsorbed onto the surface of *E. coli*. It was demonstrated by SEM that the antibacterial mechanism was membranous lysis of the bacteria (Fig. S6, ESI[†]). As reported, the hydrophobic groups of antibacterial agents can insert into the membranes of bacteria, resulting in membranous lysis.^{13,16,17} By locally enriching the hydrophobic groups of TNAB on the antibacterial supramolecular polymer, the membranous lysis of bacteria can be enhanced, thus promoting the antibacterial efficacy.

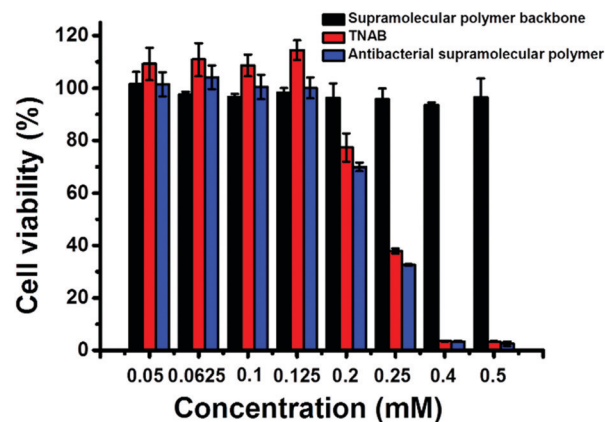


Fig. 5 The cytotoxicity of supramolecular polymer backbone, TNAB and antibacterial supramolecular polymer on mammalian cells (HaCaT).

The cytotoxicity of TNAB, supramolecular polymer backbone and antibacterial supramolecular polymer on mammalian cells was also investigated by MTT assay. A nonmalignant epithelial cell line, HaCaT, was chosen as representative cells. As shown in Fig. 5, no cytotoxicity was observed for the supramolecular antibacterial polymer, TNAB and supramolecular polymer backbone when their concentrations were lower than 0.125 mM. The antibacterial supramolecular polymer and TNAB exhibited cytotoxicity when their concentrations were higher than 0.125 mM. However, the supramolecular polymer backbone displayed no clear cytotoxicity even if the concentration was increased up to 0.50 mM. These results suggest that the fabrication of the antibacterial supramolecular polymer is a potential biocompatible strategy for further medical treatment.

Conclusions

In conclusion, we have successfully fabricated a side-chain antibacterial supramolecular polymer *via* the self-sorting strategy. The side-chain antibacterial supramolecular polymer exhibits enhanced antibacterial efficacy and controllable degradation. Besides *E. coli*, this kind of supramolecular polymeric antibacterial material could be used for killing other kinds of microbes. In addition, it is anticipated that other antibiotic reagents may also be supramolecularly polymerized through this method, thus providing a general strategy for building degradable polymer antibiotics with enhanced antibacterial efficacy to fight against drug-resistant bacteria.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by the National Natural Science Foundation of China (21434004, 21821001, 91527000) and the Tsinghua University Initiative Research Project (20181080084).

Notes and references

- 1 Y. Qian, D. Zhang, Y. Wu, Q. Chen and R. Liu, *Acta Polym. Sin.*, 2016, 1300–1311.
- 2 C. Zhu, L. Liu, Q. Yang, F. Lv and S. Wang, *Chem. Rev.*, 2012, **112**, 4687–4735.
- 3 Y. Yang, P. He, Y. Wang, H. Bai, S. Wang, J.-F. Xu and X. Zhang, *Angew. Chem., Int. Ed.*, 2017, **56**, 16239–16242.
- 4 S. E. Rossiter, M. H. Fletcher and W. M. Wuest, *Chem. Rev.*, 2017, **117**, 12415–12474.
- 5 G. D. Wright, *ACS Infect. Dis.*, 2015, **1**, 80–84.
- 6 I. B. Seiple, Z. Zhang, P. Jakubec, A. Langlois-Mercier, P. M. Wright, D. T. Hog, K. Yabu, S. R. Allu, T. Fukuzaki, P. N. Carlsen, Y. Kitamura, X. Zhou, M. L. Condakes, F. T. Szczypiński, W. D. Green and A. G. Myers, *Nature*, 2016, **533**, 338–345.
- 7 D. J. Payne, M. N. Gwynn, D. J. Holmes and D. L. Pompliano, *Nat. Rev. Drug Discovery*, 2007, **6**, 29–40.
- 8 H. Bai, X. Fu, Z. Huang, F. Lv, L. Liu, X. Zhang and S. Wang, *ChemistrySelect*, 2017, **2**, 7940–7945.
- 9 W. A. Velema, J. P. van der Berg, M. J. Hansen, W. Szymanski, A. J. M. Driessen and B. L. Feringa, *Nat. Chem.*, 2013, **5**, 924–928.
- 10 W. Szymanski, J. M. Beierle, H. A. V. Kistemaker, W. A. Velema and B. L. Feringa, *Chem. Rev.*, 2013, **113**, 6114–6178.
- 11 H. Bai, F. Lv, L. Liu and S. Wang, *Chem. – Eur. J.*, 2016, **22**, 11114–11121.
- 12 Z. Huang, H. Zhang, H. Bai, Y. Bai, S. Wang and X. Zhang, *ACS Macro Lett.*, 2016, **5**, 1109–1113.
- 13 H. Bai, H. Yuan, C. Nie, B. Wang, F. Lv, L. Liu and S. Wang, *Angew. Chem., Int. Ed.*, 2015, **54**, 13208–13213.
- 14 X. Chen, F. Wang, J. Y. Hyun, T. Wei, J. Qiang, X. Ren, I. Shin and J. Yoon, *Chem. Soc. Rev.*, 2016, **45**, 2976–3016.
- 15 X. Li, S. Lee and J. Yoon, *Chem. Soc. Rev.*, 2018, **47**, 1174–1188.
- 16 L. Chen, H. Bai, J.-F. Xu, S. Wang and X. Zhang, *ACS Appl. Mater. Interfaces*, 2017, **9**, 13950–13957.
- 17 Y. Yang, Z. Cai, Z. Huang, X. Tang and X. Zhang, *Polym. J.*, 2018, **50**, 33–44.
- 18 Y. Liu and J. A. Imlay, *Science*, 2013, **339**, 1210–1213.
- 19 M. Garland, S. Loscher and M. Bogoyo, *Chem. Rev.*, 2017, **117**, 4422–4461.
- 20 W. Kim, W. Zhu, G. L. Hendricks, D. Van Tyne, A. D. Steele, C. E. Keohane, N. Fricke, A. L. Conery, S. Shen, W. Pan, K. Lee, R. Rajamuthiah, B. B. Fuchs, P. M. Vlahovska, W. M. Wuest, M. S. Gilmore, H. Gao, F. M. Ausubel and E. Mylonakis, *Nature*, 2018, **556**, 103–107.
- 21 B. S. Li, R. Wen, S. Xue, L. Shi, Z. Tang, Z. Wang and B. Z. Tang, *Mater. Chem. Front.*, 2017, **1**, 646–653.
- 22 G. Huang, R. Wen, Z. Wang, B. S. Li and B. Z. Tang, *Mater. Chem. Front.*, 2018, **2**, 1884–1892.
- 23 P. I. O'Daniel, Z. Peng, H. Pi, S. A. Testero, D. Ding, E. Spink, E. Leemans, M. A. Boudreau, T. Yamaguchi, V. A. Schroeder, W. R. Wolter, L. I. Llarrull, W. Song, E. Lastochkin, M. Kumarasiri, N. T. Antunes, M. Espahbodi, K. Lichtenwalter, M. A. Suckow, S. Vakulenko, S. Mobashery and M. Chang, *J. Am. Chem. Soc.*, 2014, **136**, 3664–3672.
- 24 M. Zhang, P.-P. Zhu, P. Xin, W. Si, Z.-T. Li and J.-L. Hou, *Angew. Chem., Int. Ed.*, 2017, **56**, 2999–3003.
- 25 X. Li, D. Lee, J.-D. Huang and J. Yoon, *Angew. Chem., Int. Ed.*, 2018, **57**, 9885–9890.
- 26 X. Li, H. Bai, Y. Yang, J. Yoon, S. Wang and X. Zhang, *Adv. Mater.*, 2019, **31**, 1805092.
- 27 P.-Z. Chen, L.-Y. Niu, H. Zhang, Y.-Z. Chen and Q.-Z. Yang, *Mater. Chem. Front.*, 2018, **2**, 1323–1327.
- 28 L. Yang, X. Tan, Z. Wang and X. Zhang, *Chem. Rev.*, 2015, **115**, 7196–7239.
- 29 J.-F. Xu, Y.-Z. Chen, D. Wu, L.-Z. Wu, C.-H. Tung and Q.-Z. Yang, *Angew. Chem., Int. Ed.*, 2013, **52**, 9738–9742.
- 30 X. Ma and H. Tian, *Acc. Chem. Res.*, 2014, **47**, 1971–1981.
- 31 R. Sun, C. Xue, X. Ma, M. Gao, H. Tian and Q. Li, *J. Am. Chem. Soc.*, 2013, **135**, 5990–5993.
- 32 H.-Q. Peng, X. Zheng, T. Han, R. T. K. Kwok, J. W. Y. Lam, X. Huang and B. Z. Tang, *J. Am. Chem. Soc.*, 2017, **139**, 10150–10156.
- 33 D.-S. Guo and Y. Liu, *Chem. Soc. Rev.*, 2012, **41**, 5907–5921.
- 34 G. Yu, X. Zhao, J. Zhou, Z. Mao, X. Huang, Z. Wang, B. Hu, Y. Liu, F. Zhang, Z. He, O. Jacobson, C. Gao, W. Wang, C. Yu, X. Zhu, F. Huang and X. Chen, *J. Am. Chem. Soc.*, 2018, **140**, 8005–8019.
- 35 J. D. Barrio, P. N. Horton, D. Lairez, G. O. Lloyd, C. Toprakcioglu and O. A. Scherman, *J. Am. Chem. Soc.*, 2013, **135**, 11760–11763.
- 36 C. Fouquey, J.-M. Lehn and A.-M. Levelut, *Adv. Mater.*, 1990, **2**, 254–257.
- 37 U. S. Schubert, O. Hien and C. Eschbaumer, *Macromol. Rapid Commun.*, 2000, **21**, 1156–1161.
- 38 M. Burnworth, L. Tang, J. R. Kumpfer, A. J. Duncan, F. L. Beyer, G. L. Fiore, S. J. Rowan and C. Weder, *Nature*, 2011, **472**, 334–337.
- 39 J. Sautaux, L. M. Espinosa, S. Balog and C. Weder, *Macromolecules*, 2018, **51**, 5867–5874.
- 40 T. Aida, E. W. Meijer and S. I. Stupp, *Science*, 2012, **335**, 813–817.
- 41 J. Murray, K. Kim, T. Ogoshi, W. Yao and B. C. Gibb, *Chem. Soc. Rev.*, 2017, **46**, 2479–2496.
- 42 A. Harada, Y. Takashima and H. Yamaguchi, *Chem. Soc. Rev.*, 2009, **38**, 875–882.
- 43 S. Yang, A. V. Ambade and M. Weck, *Chem. Soc. Rev.*, 2011, **40**, 129–137.
- 44 T. F. A. de Greef and E. W. Meijer, *Nature*, 2008, **453**, 171–173.
- 45 X. Hou, C. Ke, Y. Zhou, Z. Xie, A. Alngadh, D. T. Keane, M. S. Nassar, Y. Y. Botros, C. A. Mirkin and J. F. Stoddart, *Chem. – Eur. J.*, 2016, **22**, 12301–12306.
- 46 J.-F. Xu and X. Zhang, *Acta Polym. Sin.*, 2017, 37–49.
- 47 K.-D. Zhang, J. T. Hanifi, Y. Zhang, A. C.-H. Sue, T.-Y. Zhou, L. Zhang, X. Zhao, Y. Liu and Z.-T. Li, *J. Am. Chem. Soc.*, 2013, **135**, 17913–17918.
- 48 Z. Zhang, Y. Luo, J. Chen, S. Dong, Y. Yu, Z. Ma and F. Huang, *Angew. Chem., Int. Ed.*, 2011, **50**, 1397–1401.
- 49 H. Wang, X. Ji, Z. Li, C. N. Zhu, X. Yang, T. Li, Z. L. Wu and F. Huang, *Mater. Chem. Front.*, 2017, **1**, 167–171.
- 50 Y. Liu, Y. Zhang, H. Zhu, H. Wang, W. Tian and B. Shi, *Mater. Chem. Front.*, 2018, **2**, 1568–1573.

- 51 X. Yan, D. Xu, X. Chi, J. Chen, S. Dong, X. Ding, Y. Yu and F. Huang, *Adv. Mater.*, 2012, **24**, 362–369.
- 52 S. Dong, J. Leng, Y. Feng, M. Liu, C. J. Stackhouse, A. Schçnhals, L. Chiappisi, L. Gao, W. Chen, J. Shang, L. Jin, Z. Qi and C. A. Schalley, *Sci. Adv.*, 2017, **3**, eaao0900.
- 53 X. Yan, Z. Liu, Q. Zhang, J. Lopez, H. Wang, H.-C. Wu, S. Niu, H. Yan, S. Wang, T. Lei, J. Li, D. Qi, P. Huang, J. Huang, Y. Zhang, Y. Wang, G. Li, J. B.-H. Tok, X. Chen and Z. Bao, *J. Am. Chem. Soc.*, 2018, **140**, 5280–5289.
- 54 Z. Huang, B. Qin, L. Chen, J.-F. Xu, C. F. J. Faul and X. Zhang, *Macromol. Rapid Commun.*, 2017, **38**, 1700312.
- 55 Y.-Y. Huang, Y. Tian, X.-Q. Liu, Z. Niu, Q.-Z. Yang, V. Ramamurthy, C.-H. Tung, Y.-Z. Chen and L.-Z. Wu, *Mater. Chem. Front.*, 2018, **2**, 1893–1899.
- 56 S. Ogi, V. Stepanenko, K. Sugiyasu, M. Takeuchi and F. Würthner, *J. Am. Chem. Soc.*, 2015, **137**, 3300–3307.
- 57 M. M. Safont-Sempere, G. Fernández and F. Würthner, *Chem. Rev.*, 2011, **111**, 5784–5814.
- 58 J.-M. Lehn, *Science*, 2002, **295**, 2400–2403.
- 59 S. Liu, C. Ruspì, P. Mukhopadhyay, S. Chakrabarti, P. Y. Zavalij and L. Isaacs, *J. Am. Chem. Soc.*, 2005, **127**, 15959–15967.
- 60 M. Hutin, C. J. Cramer, L. Gagliardi, A. R. M. Shahi, G. Bernardinelli, R. Cerny and J. R. Nitschke, *J. Am. Chem. Soc.*, 2007, **129**, 8774–8780.
- 61 T. F. A. de Greef, G. Ercolani, G. B. W. L. Ligthart, E. W. Meijer and R. P. Sijbesma, *J. Am. Chem. Soc.*, 2008, **130**, 13755–13764.
- 62 B. H. Northrop, Y. Zheng, K. Chi and P. J. Stang, *Acc. Chem. Res.*, 2009, **42**, 1554–1563.
- 63 W. Jiang and C. A. Schalley, *Proc. Natl. Acad. Sci. U. S. A.*, 2009, **106**, 10425–10429.
- 64 L. Cera and C. A. Schalley, *Chem. Sci.*, 2014, **5**, 2560–2567.
- 65 Z. Huang, L. Yang, Y. Liu, Z. Wang, O. A. Scherman and X. Zhang, *Angew. Chem., Int. Ed.*, 2014, **53**, 5351–5355.
- 66 L. Chen, Z. Huang, J.-F. Xu, Z. Wang and X. Zhang, *Polym. Chem.*, 2016, **7**, 1397–1404.