



Cite this: *Biomater. Sci.*, 2021, **9**, 4246

## Biomimetic hydrogels designed for cartilage tissue engineering

Kresanti D. Ngadimin,<sup>†</sup> Alexander Stokes,<sup>†</sup> Piergiorgio Gentile<sup>\*</sup> and Ana M. Ferreira<sup>\*</sup>

Received 31st October 2020,  
Accepted 12th February 2021

DOI: 10.1039/d0bm01852j

rscl.li/biomaterials-science

Cartilage regeneration and repair remain a clinical challenge due to the limited capability of cartilage to self-regenerate. Worldwide, the costs associated with cartilage regeneration per patient are estimated on average £30 000 for producing and supplying cells. Regenerative approaches may include the use of cell therapies and tissue engineering by combining relevant cells, scaffolds and instructive biomolecules to stimulate or modulate cartilage repair. Hydrogels have been of great interest within these fields to be used as 3D substrates to cultivate and grow cartilage cells. Currently, biomimetic hydrogels with adequate biological and physicochemical properties, such as mechanical properties, capable of supporting load-bearing capability, are yet to succeed. In this review, biomaterials' advantages and disadvantages for the manufacturing of biomimetic hydrogels for cartilage regeneration are presented. Different studies on the formulation of cartilage-like hydrogels based on materials such as gelatin, chondroitin sulfate, hyaluronic acid and polyethylene glycol are summarised and contrasted in terms of their mechanical properties (e.g. elastic modulus) and ability to enhance cell function such as cell viability and GAG content. Current limitations and challenges of biomimetic hydrogels for cartilage regeneration are also presented.

## Introduction

Articular cartilage is a non-vascularised and low cellular density connective tissue in the joints. It is frequently damaged due to injury or normal wear and tear.<sup>1</sup> Articular cartilage resists compressive forces and protects the underlying subchondral bone. It also provides a low friction surface for a diarthrodial joint to pivot. One of the most common joint diseases affecting articular cartilage is for example osteoarthritis, which affects approximately 300 million people worldwide and is the leading cause of disability among the elderly.<sup>2</sup> This condition is caused by cartilage injury in the joints due to stress, especially in the weight-bearing joints. Due to its avascular nature, low cell proliferation, and migration, repairing cartilage has been one of the challenges for improving the clinical outcome of the patient.<sup>3</sup>

Articular cartilage is made up of chondrocytes contained in the cartilage lacunae, residing in an extracellular matrix (ECM) produced by the chondrocytes. Chondrocytes reside in the cartilage in small cavities known as lacunae and reside cytoplasmically isolated from the neighbouring cells. Chondrocytes are normally rounded with a high matrix to cell volume ratio. In the cartilage, chondrocytes play roles in synthesizing and maintaining the ECM to prevent tissue deformation and supporting tissue function. They also influence epiphyseal plate growth by cell proliferation, matrix secretion, and cell volume increment during hypertrophy.<sup>4</sup>

<sup>a</sup>Faculty of Medical Sciences, Newcastle University, Newcastle upon Tyne, UK

<sup>b</sup>Faculty of Medicine, Universitas Indonesia, Indonesia

<sup>c</sup>Faculty of Science, Agriculture & Engineering, Newcastle University, Newcastle upon Tyne, UK. E-mail: ana.ferreira-duarte@ncl.ac.uk, Piergiorgio.gentile@ncl.ac.uk

<sup>†</sup>These authors have equally contributed to this work.



Ana M. Ferreira

Ana Ferreira-Duarte is a Lecturer in the School of Engineering at Newcastle University, UK. She obtained a degree in Chemical Engineering and M.Sc. in Biomedical Engineering from the Universidad Simon Bolivar (Republic of Venezuela), and her PhD in Biomedical Engineering from the Politecnico di Torino (Italy). She received the Award of High Qualification Research Doctorate by the Scuola Interpolitecnica di Dottorato for

her dissertation. She moved to the UK in 2013 and joined Newcastle University and the Arthritis Research UK Tissue Engineering Centre. Her research focuses on biomaterial design and biointerfaces, manufacturing and functionalization of biomimetic systems for tissue engineering and regenerative medicine.



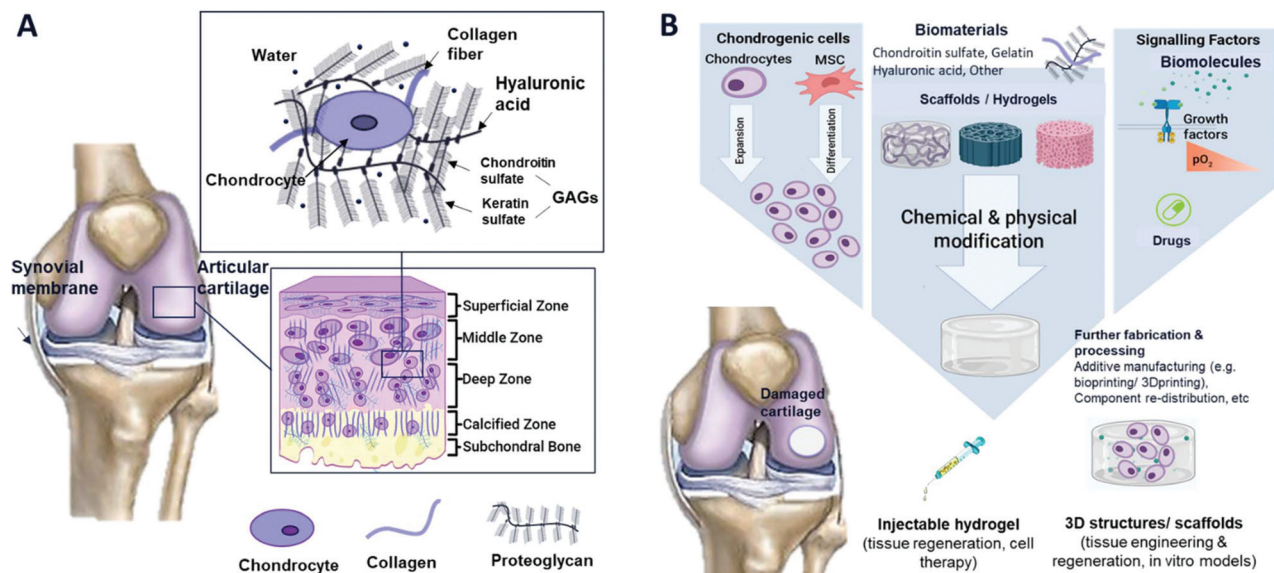


Fig. 1 Schematic illustrations of (A) cartilage composition and typical tissue zones and (B) the tissue engineering approach for cartilage repair.

The ECM is highly hydrated and contains proteoglycans (e.g. hyaluronic acid and glycosaminoglycans), collagen fibres and elastin. Glycosaminoglycans consist of chondroitin sulphate and keratin sulfate.<sup>5</sup> ECM is essential for cartilage as it plays a role in cell signalling and it can regulate cell adhesion, growth, differentiation and migration. The ECM also maintains the physiological homeostasis of the cell microenvironment.<sup>6</sup> Unlike most tissues, cartilage does not have blood vessels, nerves, or lymphatics. The composition of cartilage differs between four zones (Fig. 1A), which are mostly composed of proteoglycan content and collagen fibre alignment. In the superficial zone, collagen fibres are aligned parallel to the articulating surface, while in the middle zone, they are unaligned. In the deep zone, the fibres are radially arranged, and lastly, in the zone of calcified cartilage, an interface region between cartilage and bone is formed with the presence of mineralised fibres. The composition and organisation of each zone layer are to be considered when mimicking native cartilage tissues, as they impart distinctive zone mechanical properties, e.g. the compressive modulus increases with depth from the articular surface.<sup>7</sup>

In superficial and mid-zone cartilage, chondrocytes function to produce collagen type II, IX, and XI, and proteoglycans of the ECM. Collagen type II makes up 90–95% of the collagen in the ECM and helps to stabilize the matrix, providing tensile and shear strength to the tissues.<sup>8</sup> Collagen type IX and XI are less abundant in articular cartilage, and function to stabilize fibrillar collagen crosslinking. In the deep zone, chondrocytes are terminally differentiated and synthesize collagen type X, which plays a role in calcification.<sup>9</sup> Type X collagen is also a hallmark for proteolytic enzyme production, which breaks down the cartilage ECM and allows for vascularization and calcification of tissues.<sup>8</sup>

Tissue engineering (TE) is an interdisciplinary field that combines materials science and cell biology to improve or

replace biological tissues. The main elements that build up TE are based on cell source, scaffold, and signalling molecules (Fig. 1B). The 3D porous scaffold acts as a template for tissue formation as it provides a suitable environment for the tissues or organs to grow. For example, scaffolds used in cartilage regeneration can be differentiated into sponges, membranes, and non-woven, non-injectable and injectable hydrogels. A hydrogel is a hydrophilic polymer that is capable of holding a large amount of water.<sup>10</sup> This property of hydrogels is crucial for mimicking the high water content (up to 80%<sup>11</sup>) present in cartilage tissue. The scaffold is seeded with cells and optional signalling factors such as growth factors or external stimuli.<sup>12</sup> The use of scaffolds is also considered in other cartilage regenerative medicine approaches, such as in cell therapies like autologous or allogeneic chondrocyte implantation. The scaffold can be seeded with cartilage cells and placed in defective areas. So, the hydrogel is to be tuned to modulate cell behaviour such as cell migration and adhesion, providing temporary support for cellular function by polymer degradation.<sup>13</sup>

In cartilage tissue engineering, scaffolds or hydrogels with suitable properties to improve cellular function to regenerate cartilage and support load-bearing capability are yet to succeed. This review aims to give an overview of hydrogel usage for cartilage tissue regeneration, covering materials, techniques, and the future outlook of hydrogels as a tissue engineering approach.

## The use of hydrogels in cartilage tissue engineering

Hydrogels are attractive scaffolds as they can be structurally similar to the ECM of various tissues, and can be delivered arthroscopically, making it a minimally invasive treatment.<sup>13</sup>



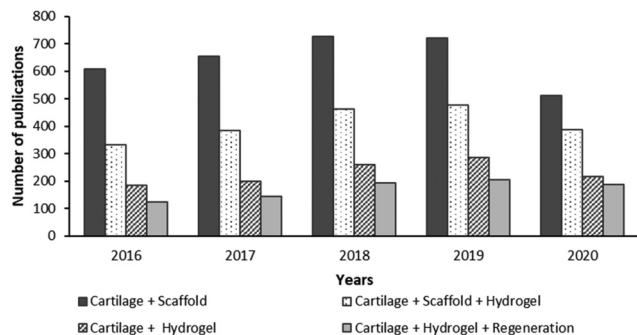


Fig. 2 The topic of research from the last five years in the “Web of Knowledge” on the use of hydrogel for cartilage tissue (last accessed on 25<sup>th</sup> September 2020).

Hydrogel properties can be tuned to a particular application including drug delivery and tissue repair. The usage of hydrogels for cartilage regeneration research has been increasing in the last decade. For instance, after a keyword search on the “Web of Knowledge” using a combination of “Scaffold”, “Cartilage”, “Hydrogel” and “Regeneration” on 25<sup>th</sup> of September 2020 (shown in Fig. 2), it was found that the number of research outputs on cartilage scaffolds on average nearly triples the number of studies on cartilage hydrogels. Based on this, the number of publications on hydrogels used as cartilage scaffolds is about 64% of the overall total of cartilage scaffold articles. Studies on hydrogels for the regeneration of cartilage have been steadily increasing up to 1.4 times between 2016 and 2020, representing about 74% of the total number of studies of cartilage hydrogel outputs.

Hydrogels offer the advantage of being tunable, so their properties can be modified to suit the application requirements. Some of the adjustable factors are the composition of the hydrogel, degree of crosslinking and methods of crosslinking that make the structure rigid, and density of the cells in the hydrogel. Ideally, for cartilage applications, the hydrogel composition should mimic the ECM whilst being able to withstand mechanical stress and loads, especially in load-bearing joints.<sup>14</sup> For instance, desired compressive stress between 0.4 and 2.0 MPa, tensile stress between 5 and 25 MPa, and shear stresses in the order of 3 MPa have been reported.<sup>15–17</sup>

## Biomimetic hydrogels for cartilage TE

### Materials used to create biomimetic hydrogels

Broadly, hydrogels can be differentiated, according to the nature of the material composition, into natural, synthetic and biosynthetic. The natural hydrogels are commonly used for cartilage regeneration purposes;<sup>50</sup> these include protein-based, polysaccharide-based, and decellularized hydrogels. The protein hydrogel includes collagen, elastin, fibrin, gelatin, and silk fibroin, while the polysaccharide hydrogel includes, for instance, glycosaminoglycans, alginate, chitosan, and agarose.<sup>51</sup> In addition, biodegradable synthetic materials have

been explored such as poly(ethylene glycol) (PEG), poly(*N*-isopropylacrylamide) (pNiPAAM), and poly(vinyl alcohol) (PVA). In addition, polyesters such as polylactide acid (PLA) and polycaprolactone (PCL) and its derivatives are incorporated into hydrogels to reinforce mechanical properties or as carriers for drug delivery.<sup>52</sup> In Table 1, some of the common materials used for tissue engineering are summarised, reflecting their strengths, weaknesses and potential applications. In the last 5 years, innovative bioinspired hydrogels for cartilage applications have been formulated including mussel-inspired polydopamine-incorporated hydrogels<sup>32,53,54</sup> to facilitate cell adhesion and tissue integration, incorporating sugar-based additives such as manuka honey to provide antibacterial properties<sup>55</sup> and improved mechanical properties,<sup>56</sup> and to mimic biological structures<sup>57,58</sup> and networks<sup>59</sup> for improved mechanical and biological performance.

### The use of crosslinking in biomimetic hydrogels

In hydrogels, the degree of crosslinking can control the swelling properties, while increasing the stability, and controlling the degradation rates and the level of porosity.<sup>60</sup> These are fundamental properties for tissue regeneration, since these will influence cellular function and the ability to provide support for new tissue formation. For instance, uncontrolled hydrogel swelling causes hydrostatic pressure in the surrounding tissue, which can cause inflammation and limited regeneration. The hydrogel polymer(s) chains can be crosslinked covalently or non-covalently (*i.e.* ionic bonds) involving either a chemical or physical reaction.<sup>61</sup> Chemical crosslinkers are commonly used to establish covalent bonds between polymer chains, whereas physical crosslinkers facilitate physical interactions between chains or trigger chemical polymerizations. Cross-linking with free-radical polymerizations or copolymerization is commonly used by reacting hydrophilic monomers to multifunctional cross-linkers to produce cross-link junctions and physical interactions. The condensation reaction is often used to crosslink hydroxyl groups or amines with carboxylic acids present in proteins and some polysaccharides. For instance, the carbodiimide reaction may use the *N,N*-(3-dimethylaminopropyl)-*N*-ethylcarbodiimide (EDC) reagent to crosslink water-soluble polymers with amide bonds. The *O*-acylisourea intermediate, the carbodiimide activated acid, becomes deactivated fast, hence hindering the occurrence of amine reactions. The addition of *N*-hydroxysuccinimide (NHS) allows for more stable esters compared to the *O*-acylisourea intermediate and more reactivity towards amines.<sup>62</sup>

*In situ* crosslinking of injectable hydrogels allows for a minimally invasive procedure and cell encapsulation and transplantation, and enables the ability to match irregular defects.<sup>6</sup> Different crosslinking methods can be used to prepare injectable hydrogels, including physical and chemical crosslinking<sup>63</sup> such as photo-crosslinking, enzymatically crosslinked hydrogels, ion- or pH-sensitive hydrogels, click chemistry, *etc.* For instance, recent works on click-crosslinked modified HA hydrogels for cartilage tissue engineering have shown suitable mechanical properties and porous structures leading





**Table 1** Comparison of strengths and weaknesses of different biomaterials used in cartilage tissue engineering

Natural material			
Material	Type	Strengths	Weaknesses
Collagen	Protein-based	Low antigenicity, low inflammatory response, excellent biological properties, biodegradability and biocompatibility <sup>18–20</sup>	High cost, thrombogenic potential, low mechanical strength and modification difficulty <sup>21,22</sup>
Gelatin	Protein-based	Low cost, minimal immunogenicity, degradability and compatibility <sup>23</sup>	Stability decreases at high temperatures <sup>24</sup>
Silk fibroin	Protein-based	Excellent mechanical properties, low immunogenicity <sup>25</sup> and low thrombogenicity <sup>26</sup>	Source difficulty and slow gelation <sup>27</sup>
Glycosaminoglycans (GAGs)–hyaluronic acid (HA) and chondroitin sulphate (CS)	Polysaccharide-based	Mimics cartilage ECM composition, biodegradable, <sup>28</sup> reabsorbable, easy to scale up, <sup>29</sup> and binds signalling factors <sup>30</sup>	Rapid degradation <i>in vivo</i> and require crosslinking to be stable <sup>31,32</sup>
Alginate	Polysaccharide-based	Non-toxic, non-inflammatory and rapid gelation <sup>33,34</sup>	Poor cell adhesion and mechanical properties <sup>35</sup>
Chitosan	Polysaccharide-based	Anti-bacterial, low cost, biocompatible and tuned biodegradability <sup>36</sup>	Poor mechanical properties <sup>37</sup>
Decellularized hydrogels	Protein-based	Recreate native ECM cartilage <sup>38</sup> and can deliver biochemical signal	Require complex processes and potential immunogenicity <sup>38</sup>
Synthetic material			
Material	Strengths		Weaknesses
Poly(ethylene glycol) (PEG)	Biodegradable and non-immunogenicity <sup>39</sup> adjustable properties <sup>40</sup>		Lack of adhesion support <sup>40</sup>
Poly(glutamic acid) (PGA)	Biodegradable by hydrolysis, thermoplastic, adjustable mechanical properties, <sup>41</sup> porosity <sup>42</sup> and localized inflammation <sup>43</sup>		Weak physically crosslinked gel, hydrolysis product can cause inflammation and fast degradation <sup>44</sup>
Poly(lactic acid) and copolymers	Biodegradable by hydrolysis, <sup>45</sup> good mechanical properties <sup>46</sup> and solubility in organic solvents, <sup>47</sup> and reinforce hydrogels <sup>48,49</sup>		Hydrolysis by-products can cause inflammation <sup>44</sup>

to high GAG expression and chondrogenic differentiation of human periodontal ligament stem cells (hPDLSCs).<sup>64</sup> Similarly, enzymatic crosslinking of hydrogels has drawn significant attention in the development of injectable hydrogels for tissue engineering, as it enables a quick gelation under physiological conditions with high specificity and low cytotoxicity.<sup>65</sup> Optimal enzyme selection still needs to be achieved to maintain cell bioactivity during encapsulation.<sup>66</sup> Some of the recent works on enzymatically crosslinked collagen-HA hydrogels showed promising results as injectable bone marrow mesenchymal stem cell (BMSC)-laden hydrogels for cartilage tissue regeneration.<sup>67</sup> These results were observed *in vitro* and *in vivo* when implanted in rats' cartilage defects, in which the hydrogel supported BMSC chondrogenic differentiation and hyaline cartilage repair. Similarly, studies on enzyme-crosslinked biomimetic hydrogels based on gelatin enriched with the cartilage extracellular matrix evidenced promising results in hyaline cartilage formation and GAG content in rabbit knee joint models.<sup>68</sup>

Another approach is interpenetrating network (IPN) hydrogels, in which two or more polymers in the networks are partly interlaced on the molecular scale within the matrix; these are not covalently bonded and these polymers cannot be separated without breaking their chemical bonds in the matrix.<sup>69</sup> Multiple networks such as IPN are better than a single network in terms of mechanical strength and swelling ability.<sup>70,71</sup> Broadly, the high water content tends to reduce the mechanical properties of single network hydrogels. Thus, novel approaches such as the “double network” (DN) have

been lately developed to improve their mechanical performance. This type of IPN hydrogel consists of a preparation first of a densely cross-linked polyelectrolyte network, followed by a neutral and loosely cross-linked (fully swollen) network.<sup>72</sup> This approach, initially promoted by Gong *et al.*,<sup>73</sup> has led to promising results towards mimicking the native cartilage mechanical properties,<sup>74</sup> including stiffness, high resistance to wear, and compression limit.<sup>75,76</sup> The polymer DN approach has been applied as a tissue-reinforcement mechanism by interpenetrating the damaged cartilage tissue, showing an increase of the tissue's equilibrium compressive modulus and wear resistance, while maintaining the cartilage volume when subject to harsh articulation conditions.<sup>77</sup> DN synthetic hydrogels have been used to mimic native mechanical properties and lubricity of cartilage obtaining exceptional cartilage-like properties suitable even for repairing chondral defects in the load-bearing regions of the body.<sup>76</sup> Lastly, DN hydrogels can be also enzymatically cross-linked for repairing cartilage. This was demonstrated recently by encapsulating human articular chondrocytes into biosynthetic DN hydrogels for the 3D bioprinting of cartilage engineering constructs, obtaining highly cytocompatible hydrogels with fast kinetics when compared to compositionally similar materials.<sup>78</sup>

## Mimicking cartilage composition

Cartilage is a highly hydrated tissue mostly composed of a combination of proteins and GAGs, such as collagen, HA, CS,



and KS. In particular, CS and KS (keratan sulfate) are two types of glycosaminoglycans (GAGs) that are normally attached to a protein core forming proteoglycans namely aggrecan.<sup>5</sup> This KS/CS proteoglycan is linked to the HA core protein to form a larger proteoglycan aggregate. In particular, CS and HA are two types of glycosaminoglycans (GAGs) that are normally attached to a protein chain forming the proteoglycans found in cartilage.<sup>79</sup> Gelatin has been widely used in TE research as it is a derivate of collagen, a prominent ECM molecule of cartilage that has adhesion sites to chondrocytes.<sup>80</sup> The combination of CS, HA, and gelatin displays great potential for cartilage TE as derivatives of the ECM. However, like most natural polymers, they lack good mechanical properties. To develop biomimetic hydrogels with improved mechanical properties, these are usually combined with water-soluble synthetic polymers, *e.g.* such as polyethylene glycol (PEG).<sup>81</sup> Below, a further description is given of these materials used for cartilage regenerative approaches.

### Chondroitin sulphate

Chondroitin sulphate (CS) is a polysaccharide molecule and the most abundant GAG found in the human body, which makes up 80% of GAGs in adult articular cartilage.<sup>82,83</sup> CS is a linear sulphated GAG with repeating D-glucuronic acid and D-N-acetylgalactosamine units.<sup>84</sup> It has the ability for tissue integration and exhibits an anti-inflammatory response.<sup>85</sup> With ageing, the content of CS in cartilage decreases due to degeneration.<sup>86</sup> CS is reported to be more effective in improving MSC chondrogenesis compared to heparan sulphates, especially in low stiffness. This is beneficial because a new matrix deposition accompanied by increasing mechanical properties occurs due to the neocartilage deposited by the cell.<sup>87</sup> Due to its high charge density, it has a high water content, which results in mechanical weakness. Hence, CS is usually combined and crosslinked with other materials for enhanced mechanical properties.<sup>82,88,89</sup> Chondrogenic regeneration has been widely studied using CS-based hydrogels. Previous studies on CS combined with pullulan hydrogels showed good viability of the encapsulated chondrocytes, displaying enhanced chondrogenesis in both self-crosslinked and enzymatically crosslinked hydrogels.<sup>90,91</sup> CS-based hydrogels have been shown to exhibit the highest gene expression and matrix accumulation throughout the cartilage zones compared to HA- and type I collagen-based hydrogels.<sup>92</sup>

### Hyaluronic acid

Hyaluronic acid (HA) is a non-sulphated GAG with a repeating disaccharide pattern, which is distributed within cartilage. In cartilage formation, HA is reported to induce MSC differentiation into chondrocytes, to maintain chondrocyte phenotype, and to increase the ECM deposition in cartilage.<sup>116</sup> However, the *in vivo* use of HA remains a challenge due to unsatisfactory cell adhesion ability as it can be degraded by hyaluronidase, nitrogen and reactive oxygen. It can induce inflammation due to foreign objects.<sup>93</sup>

### Gelatin

Gelatin is a biodegradable natural polymer with single-stranded protein from collagen as a result of partial hydrolysis, preserving Arg-Gly-Asp (RGD) motifs for cells to adhere to.<sup>94,95</sup> It has been widely used in tissue engineering applications, as it is a low-cost polymer with minimal immunogenicity and tunable degradability.<sup>51</sup> Furthermore, it is easily soluble in water at 37 °C and amphoteric. Gelatin consists of fractions derived from collagen alpha chains, maintaining a typical aminoacidic sequence of proline, hydroxyl proline and glycine.<sup>96</sup> Promising results for *in vitro* MSC proliferation have been shown in the Pierce *et al.* study, where they use a gelatin-based hydrogel with few modifiable mechanical properties at various concentrations of ethyl lysine diisocyanate. Bone marrow-derived MSCs were viable for nine days and displayed low toxicity.<sup>97</sup> Hydrogels using bovine-sourced GEL-MA crosslinked with UV polymerisation displayed the most similar environment to native cartilage after 28 days of culture compared to porcine-derived GEL-MA.<sup>98</sup> Moreover, the addition of gelatin to other composite materials, such as alginate, has shown to increase their viability and chondrogenesis compared to alginate alone.<sup>99</sup>

The use of synthetic and water-soluble polymers such as PEG has become attractive due to their biocompatibility and ability to prevent the nonspecific absorption of protein and neutral charge.<sup>100</sup> They can act as spacer agents, hence resulting in a more effective and controllable way to link two molecules.<sup>81</sup> PEG is the most used synthetic hydrogel for tissue engineering, given its inert nature chemically and physically.<sup>101</sup> It is also biodegradable and non-immunogenic. PEG also displays a non-toxic and highly soluble nature with good mechanical properties.<sup>102,103</sup>

## Biomimetic hydrogels: mechanical and biological properties

Biomimetic hydrogels might mimic cartilage ECM composition and/or organisation to achieve biological and mechanical properties similar to those of the native tissue. For instance, natural materials such as CS and gelatin are non-toxic with tunable biodegradability; however, they have poor mechanical properties, which limit their use for tissue engineering.<sup>104</sup> For this reason, the combination of natural materials with synthetic materials is used for achieving improved overall hydrogels' biological and mechanical properties. The reported compressive modulus of articular cartilage<sup>105</sup> is 0.02–1.16 MPa in the superficial zone and 6.44–7.75 MPa in the deep zone,<sup>7</sup> while in osteoarthritic cartilage, it may range from 2 MPa to 30 MPa.<sup>17</sup> A summary of selected works, in which natural materials such as CS, gelatin and HA are combined with synthetic ones such as PEG, is shown in Table 2 and extended to Fig. 3.

Data related to mechanical (*i.e.* compressive modulus) and biological properties (*i.e.* cell viability and GAG/DNA content)





**Table 2** Summary of selected hydrogels based on PEG, CS, HA and gelatin for cartilage regeneration

Hydrogel	Crosslinkers	Time-point	Cells	Findings	Viability, ECM Production ( $\mu\text{g } \mu\text{g}^{-1}$ ), compressive modulus
CS-based (with graphene) <sup>106</sup>	EDC/NHS	3 weeks	MSCs	EDAG-CS porous hydrogels exhibit higher mechanical properties, but degrade slower than CS-CS. EDAG-CS and CS-CS produce type II collagen and MSCs do not differentiate to endochondral ossification	Cell viability and ECM production not reported Compressive modulus: 1.12 kPa
Carboxymethylated pullulan CMP-TA/CS-TA <sup>90</sup>	Enzymatic crosslinking (horseradish peroxidase and $\text{H}_2\text{O}_2$ )	14 days	Porcine articular chondrocytes	Hydrogel with a CMP-TA/CS-TA weight ratio of 3/1 provided best host tissue-mimetic microenvironment.	Viability: 80–95% (CMP-TA), >95% (CMP-TA/CS-TA) ECM production not reported Compressive modulus (CMP-TA): 0.96 kPa
GEL-based <sup>107</sup>	UV photo-polymerization	3 days, 4 weeks	Chondrocytes	Supplementation of HA to increase viscosity and PCL polymer for structural support enables the build-up of a layered hydrogel structure. Cell viability detected until 28 days using GAG/DNA.	Viability: $73 \pm 2\%$ (GEL-MA), $82 \pm 8\%$ (GEL-MA-HA) (day 3) GAG/DNA: $7.1 \pm 3.3$ (GEL-MA), $10.5 \pm 5.2$ (GEL-MA-HA) (week 4) Compressive modulus: 32.28–53.54 kPa (GEL-MA)
CS-PEG <sup>108</sup>	UV photo-polymerization	24 hours, 3 weeks	Juvenile, adult, and osteoarthritic chondrocytes	7% w/v of PEGDA and 3% w/v. Deposition of ECM and long-term cell viability are reported.	Viability: 94% ECM production not reported Compressive modulus: 0.73–1.04 kPa (day 1, week 3)
CS-PEG <sup>109</sup>	Photo-polymerization	3 weeks	Neonatal bovine chondrocytes	Dual gradient hydrogel with interconnected chambers (20% w/v PEG, 3% w/v CS; zone 1; to 2% w/v PEG, 8% w/v CS; zone 5) with better mechanical properties, cell proliferation and matrix deposition than CS hydrogel gradient alone.	Viability: >90% in all zones (7 days) GAG/DNA: 40.58–53.72 kPa (zone 1–zone 5) Compressive modulus: 9.2 kPa–124.7 kPa (zone 1–zone 5)
CS-PEG PEG-CS-MMP-pep PEG-HA <sup>110</sup>	UV photo-polymerization	2, 4, 6 weeks	D1 mouse bone marrow progenitor cell	Higher collagen II content was detected in the superficial layer (PEG : CS : MMP-pep), collagen X content and GAG production were increasing from the superficial layer, transitional (PEG : CS) to the deep layer (PEG : HA) mimicking the cartilage layer.	Viability: 86% (PEG-CS-MMP-pep), >95% (CS-PEG), 84% (PEG-HA) GAG/DNA: PEG-CS-MMP-pep: 2.6; CS-PEG: 2.8; PEG-HA: 6.6 (2 weeks) Compressive modulus: PEG-CS-MMP-pep: 199.71 (120–209 kPa), CS-PEG: 203.95 (121–270 kPa); PEG-HA: 942.83 (271–1227 kPa)
CS-PEG <sup>111</sup>	EDC/NHS	24 hours (in vitro) 4 weeks (in vivo)	Bovine articular chondrocytes	Cells within hydrogel retain viability and metabolically active, minimal inflammatory response compared to PEG, stronger adhesion compared with fibrin <i>in vivo</i> .	Viability: 93–96% ECM production not reported Compressive modulus: 11.31–22.28 kPa
CS-PEG <sup>112</sup>	UV photo-polymerization	24 hours, 3, 6 weeks	MSCs	PEG-CS gels have 10 times stronger adhesion to cartilage tissue compared to fibrin, and decreased inflammatory response compared with PEG.	Viability: 79% (PEG), 84% (CS-PEG) (24 hours) GAGs/DNA: PEG: 10.75 (week 3), 20.12 (week 6); CS-PEG: 18.11 (week 3), 36.18 (week 6)
PEG-LA-DM PEG-DM <sup>113</sup>	UV photo-polymerization	6 weeks (in vitro) 6, 12, 18 weeks (in vivo)	Juvenile swine articular chondrocytes	Encapsulated chondrocytes in 60/40 and 70/30 PEG-LA-DM/PEG-DM polymer ratios Improved cartilage matrix formation of aggrecan and collagen type II/VI	Compressive modulus not reported Cell viability and ECM production not reported Compressive modulus: 60–670 kPa (ref. 92)
PEG-HA <sup>114</sup>	Enzymatic crosslinking (HRP and $\text{H}_2\text{O}_2$ ) and Diels-Alder click chemistry	7 days	Chondrogenic teratocarcinoma cells	Enzymatic crosslinking hydrogels result in 5 minutes of gelation time, has great shape memory and anti-fatigue properties	Viability: >95% No ECM production reported Compressive modulus: 60.7–109.4 kPa

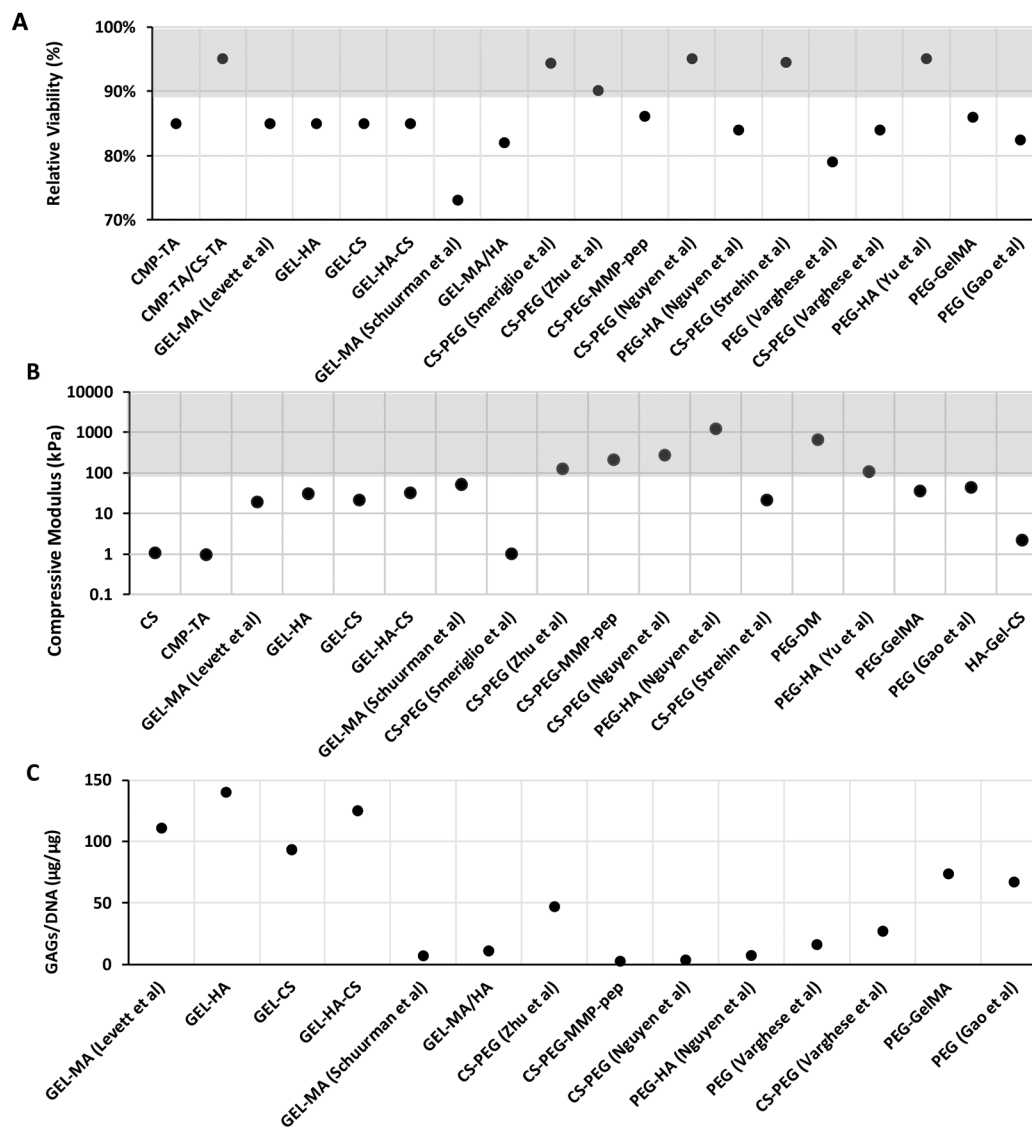


Table 2 (Contd.)

Hydrogel	Crosslinkers	Time-point	Cells	Findings	Viability, ECM Production ( $\mu\text{g } \mu\text{g}^{-1}$ ), compressive modulus
PEG-GelMa	Photo-polymerization	7 days, 3 weeks	Human MSCs	Inkjet bioprinted MSCs of PEG-MA show better mechanical properties than PEG, increased 63% under chondrogenic differentiation after 21 days.	Viability: 85.87% (PEG-GelMa), 82.43% (PEG) GAGs/DNA: 73.81 (PEG-GelMa), 67.64 (PEG) (7 days) Compressive modulus: 36.70 kPa (PEG-GelMa), 45.31 kPa (PEG) Viability: 10% CS-gelatin (79% MTT); Compressive modulus: not measured.
PEG <sup>115</sup>	EDC/NHS and click chemistry	1, 3 and 7 days	Fibroblasts and macrophages	Overall good cytocompatibility, mimicking cartilage ECM composition	ECM production: not measured Viability: not measured quantitatively. Compressive modulus: trilayer $\mu\text{RB}$ up to 456 kPa.
GEL-CS <sup>117</sup>	Chemical crosslinking (glutaraldehyde, dithiothreitol/2-propanol); and photo-crosslinking (UV-light)	21 days	Human mesenchymal stem cells (MSCs)	Spatially patterned $\mu\text{RB}$ scaffold enabled MSCs to produce cartilage with biomimetic zonal biochemical and mechanical properties	ECM production: sGAG per d.w trilayer $\mu\text{RB}$ up to 0.08 $\mu\text{g } \mu\text{g}^{-1}$ (1.5–7.5% dry weight) Viability: not measured quantitatively. Compressive modulus: up to 25 kPa (8.5/1.5 ratio mGL/mHA) ECM production: up to 17 $\mu\text{g}$ GAG/construct
GEL-HA <sup>118</sup>	Photo-crosslinking (UV-light)	Up to 8 weeks	Human bone marrow-derived mesenchymal stem cells (hBMSCs) and <i>in vivo</i> (New Zealand white rabbits)	MSCs chondrogenesis, scaffolds at 9 : 1 (% w/v) ratio mGL/mHA lowest hBMSC hypertrophy and highest glycosaminoglycan production, supported cartilage formation <i>in vivo</i> after 12 weeks	Cell viability: about 98%. Storage modulus ( $G'$ ) = 1 kPa. ECM production: no reported <i>in vitro</i> but <i>in vivo</i> (about 70 $\text{mg g}^{-1}$ LDITM scaffold and 200 $\text{mg g}^{-1}$ for Exp) Viability not measured quantitatively; cell proliferation decreases in hydrogels rich in HA. Compressive modulus ( $G'$ ) up to 789 $\pm$ 220 Pa. ECM production = GAGs about 80% in the 30/70 mixture and HA gel. Viability not measured quantitatively; cell proliferation increases in CCH hydrogels. Compressive modulus increases (CCH about 51.53 $\pm$ 0.54 kPa (ref. 122)). GAG/DNA ratio about 4 (7 days, approx. 6 $\mu\text{g } \mu\text{l}^{-1}$ ) Cell viability and ECM production not reported or tested Compressive modulus: 1.62–2.21 kPa Viability not measured quantitatively; cell number increases overtime. Compressive modulus $\sim$ 7 kPa ECM production: not measured Viability: 80–90% GAGs/DNA: 110.9 (GEL-MA), 140 (GEL-HA), 92.7 (GEL-CS), 125.3 (GEK-HA-CS) (week 8) Compressive modulus: 20.17 kPa (GEL-MA), 31.08 kPa (GEL-HA), 21.66 kPa (GEL-CS), 32.57 kPa (GEL-HA-CS)
GEL-HA <sup>119</sup>	Photo-crosslinking (UV-light)	1, 4, 7 days	Chondrocytes and <i>in vivo</i> (nude mice)	At a relatively low cell-seeding concentration, homogeneous tubular cartilage regenerated with a tracheal shape, mechanical strength and cartilage ECM deposition	
GEL-HA <sup>120</sup>	Enzymatic crosslinking (HRP and $\text{H}_2\text{O}_2$ )	Up to 14 days	Mesenchymal stem cells (MSCs)	70% HA and 30% gel most promising for chondrogenesis, best mechanical properties	
Collagen-CS-HA (CCH) <sup>121</sup>	Chemical crosslinking (Genipin, 0.75 mM)	4 weeks	Allogeneic chondrocytes ( <i>in vivo</i> Rabbits model)	CCH hydrogel provides structural and mechanical similarity to cartilage; used as a carrier of chondrocytes; helps cell growth and matrix synthesis	
HA-GEL-CS <sup>1,23</sup>	Diels-Alder click chemistry	N/A	N/A	HA-furan GEL-furan, MAL-PEG-MAL	
HA-GEL-CS <sup>1,24</sup>	Click chemistry (Cu(I) as the catalyst)	Up to 7 days	Chondrocytes	HA-GEL-CS with EDC NHS Good reactivity under very mild conditions by click-chemistry. <i>In vitro</i> cell culture confirmed that chondrocytes could adhere and proliferate on the hydrogel.	
GEL-MA GEL-HA	Photo-crosslinking (UV light)	1 day, 5 and 8 weeks	Human chondrocytes	The addition of CS and HA to GEL-MA can enhance the differentiation, improved mechanical properties, and ECM distribution. Significant COL2A1 expression	
GEL-CS GEL-HA-CS <sup>1,25</sup>					

CS: Chondroitin sulfate; CMP: Carboxymethyl pullulan; DM: Dimethylacrylate; EDAG: Ethylenediamine graphene; GEL: Gelatin; GELMA: Gelatin methacrylates; HA: Hyaluronic acid; LA: 4, 5 lactic acid; MA: Methacrylates; MMPpep: Matrix metalloproteinase-sensitive peptides; PEG: Polyethylene glycol; TA: Tyramine.





**Fig. 3** Compressive modulus, viability, and GAG/DNA of selected hydrogels. (A) Cell viability; (B) compressive modulus; and (C) GAG/DNA of hydrogels for cartilage regeneration; gray-shaded areas indicate the desired value for cartilage applications.

of biomimetic hydrogel studies were collected from different journal databases (PubMed, Web of Science, and Google Scholar). From this review, it was found that most of the hydrogels found in the literature have a compression modulus ranging from 10 to 1000 kPa, meaning that formulated hydrogels are below cartilage values by at least a factor of 10 (Fig. 3A). Particularly, it can be observed that cell-free hydrogels based on PEG-HA<sup>110</sup> (217–1227 kPa) show the highest compressive modulus when compared to PEG-DM<sup>113</sup> (60–670 kPa) and CS-PEG<sup>110</sup> (121–270 kPa). Interestingly, materials based on CS-PEG can show a very low compressive modulus (e.g. 0.73 kPa);<sup>108</sup> this can be improved by varying the cross-linking method.<sup>109–111</sup> Increased PEG concentration will result in a stiffer hydrogel.

The hydrogel should provide to the cells a suitable micro-environment that stimulates ECM production and new tissue

formation. For instance, scaffolds that are too stiff can affect biological behaviour, such as changing the phenotype of the cells and driving MSC differentiation into bone cells.<sup>126,127</sup> Moreover, it was found that by increasing substrate stiffness, chondrocyte ECM production is down-regulated while promoting adhesion and stress fibre formation.<sup>128,129</sup> However, if the modulus is not adequate in early time points, chondrocyte will produce ECM that can strengthen the hydrogel structure over time and withstand higher compressive forces.<sup>130,131</sup>

Data on cellular viability (using LIVE/DEAD assays) collected from 24 hours up to 7 days following cell seeding are shown in Fig. 3B. In general, hydrogels show good cell viability (higher than 70%), particularly those based on proteoglycans like CS and HA. From relative viability data, the overall high viability was shown for hydrogels based on CMP-TA/CS-TA,<sup>90</sup> CS-PEG,<sup>108,110,111</sup> and PEG-HA,<sup>123</sup> evidencing higher survival





(>90%) when compared to hydrogels such as GEL-MA<sup>107</sup> and PEG<sup>112</sup> (<80%). Particularly, based on the latter, GEL-MA showed the lowest cell viability amongst the group, in contrast to other gelatin-based hydrogels.<sup>132</sup> This effect may be due to the methacrylate process, which causes cytotoxicity. Methacrylate toxicity has been reported in several *in vitro* studies where glutathione (GSH), a major antioxidant that prevents oxidative stress, was removed. Increased oxidative stress caused by adduct formation of methacrylate results in cell toxicity.<sup>133,134</sup> Regarding synthetic PEG-based hydrogels, these do not contain cell adhesion motifs and so increasing the PEG concentration or polymer block length in hydrogels might result in decreased or impaired cell adhesion and protein adsorption.<sup>135,136</sup> GAG/DNA content is presented as the total accumulated GAG content normalised to the total DNA content of a selection of biomimetic hydrogels in Fig. 3C. In terms of ECM production, the gelatin-based hydrogel seems to stimulate GAG secretion, except for GEL-MA.<sup>107</sup> The gelatin-based hydrogel showed the highest levels of GAG/DNA deposition; particularly, GEL-HA had the highest GAG accumulation, followed by GEL-HA-CS.<sup>125</sup> The use of HA has been shown to enhance ECM remodelling into a more ordered collagen deposition, and increased the mRNA expression of cartilage-specific genes.<sup>137,138</sup> Consistent results were shown where the addition of HA produces a higher GAG content.<sup>107,110,125</sup> However, it appears to be concentration-dependent, where the chondrogenic properties are only shown at low concentrations, while no effect or a negative effect on chondrogenesis is observed at higher HA concentrations.<sup>107</sup>

In contrast, the lowest GAG/DNA production was found when the cells were incubated in hydrogels containing PEG.<sup>110–112</sup> One way to overcome this problem is to incorporate other polymers. Varghese *et al.* have shown that incorporation of CS into PEG hydrogels results in enhanced chondrogenic gene expression and cartilage matrix production compared to PEG alone.<sup>112</sup> Moreover, Zhu *et al.* hypothesised that a stiffer hydrogel could be made by increasing the PEG and CS concentrations in a layer-by-layer manner, resulting in more ECM production using a mechanical gradient hydrogel *via* cellular remodelling of the ECM by degradation.<sup>109</sup> Interestingly, the combination of GEL-MA and PEG favours ECM production and promotes MSC chondrogenic differentiation.<sup>115</sup> Bryant *et al.* reported that incorporation of degradable crosslinkers can promote GAGs to diffuse out of the gel without sacrificing the mechanical properties.<sup>139</sup> In contrast, studies have suggested that CS can inhibit ECM production, despite it not impacting the chondrocyte viability.<sup>109,112</sup> This phenomenon may be caused by the negative charge of CS that attracts free cations from the culture medium, which increases hydrogel osmolarity and impacts cell growth negatively.<sup>140</sup> Moreover, the addition of signalling molecules such as TGF- $\beta$ 1 can be considered for future research to improve cellular function such as cell proliferation and ECM secretion in synthetic-based hydrogels.<sup>141</sup>

In the last few years, improved cartilage ECM-like hydrogels based on CS, HA and gelatin have been formulated in the

absence of synthetic polymers such as PEG. Improved mechanical and biological performance has been achieved by exploiting the recent advances in physical and chemical crosslinking including click chemistries, photo-crosslinking, enzyme-mediated crosslinking, and interpenetrating double networks. Mechanical properties similar to native cartilage have been obtained for biomimetic hydrogels based on ECM-derived proteins,<sup>121,125</sup> achieving a compressive Young's modulus up to 456 kPa for spatially patterned  $\mu$ RB scaffolds based on CS-GEL hydrogels.<sup>117</sup> In this context, excellent mechanical and biological performance including GAG deposition and cellular viability have also been obtained for hydrogels that combine ECM-derived materials such as HA and GEL.<sup>119,121,125</sup> These properties were achieved by combining the biological cues present in the native cartilage ECM while reinforcing their structure with the presence of non-toxic crosslinking strategies without compromising hydration or cyto-/biocompatibility. In general, naturally derived biomaterials and combined ECM proteins in hydrogels (*e.g.* CS, HA, gelatin) are known as ideal biomimetic sources for cartilage tissue engineering. However, some of the key limitations, including weak mechanical properties for mimicking the surrounding tissues and control of structure and degradation rates, have limited their applications. In this overview, we have shown that recent advances in chemical or physical modifications and fabrication methods are capable of overcoming some of these limitations, demonstrating that these materials can mimic native ECM tissues and support cartilage regeneration while showing superior functional performance when compared to single or biosynthetic formulations.

## Future perspective on cartilage tissue engineering

For the past 5 years, there has been growing interest in hydrogel research for cartilage regeneration. Moreover, it has been shown that hydrogels can provide a suitable environment for chondrocytes and MSCs to grow from *in vitro* and *in vivo* research. Hydrogels capable of mimicking properties and biological activities, structure and organisation of the native tissue are needed for developing TE strategies, disease models and cell therapies.

### *In vitro* cartilage tissue models

Zonally stratified structures similar to native cartilage can be achieved by exploiting combinations of materials and composite hydrogels processed additively. Therefore, a gradient hydrogel processing technique, such as bioprinting and controlled fluid mixing, allows the creation of multiple layers with a physical and chemical composition that mimics cartilage zones.<sup>142,143</sup> Biomimetic multiphasic hydrogels and structures have been developed to mimic the native osteochondral tissue properties,<sup>144</sup> including monophasic, bi-phasic and tri-phasic structures. For instance, mussel-inspired hydrogels with a bilayer structure have shown potential to repair osteochondral



defects following implantation in rabbit knee joints.<sup>145</sup> Another example is the biphasic CAN-PAC hydrogel for the regeneration of osteochondral defects prepared by thermally initiated free radical polymerization, which showed a low inflammatory response and ingrowth of newly formed tissue when subcutaneously implanted in rats.<sup>146</sup> Moreover, advances in tissue engineering by combining hydrogels and bioprinting technologies to manufacture relevant cellular microniches present new exciting avenues for tissue modelling, ageing and disease mechanism discovery and therapy towards reducing the need for costly and unethical animal models. Photo-cross-linkable GEL-HA has been fabricated as a porous scaffold for cartilage repair with a suitable internal pore structure and high mechanical strength *via* photocuring 3D printing and lyophilization.<sup>147</sup> The encapsulation of chondrocytes into the scaffolds promoted mature cartilage regeneration with a typical lacunae structure and cartilage-specific ECM both *in vitro* and *in vivo*. Recent works on the bioprinting of biomimetic hydrogels for cartilage applications showed a great interest in using functionalised natural components<sup>148</sup> such as gelatin, chondroitin sulphate, and hyaluronic acid towards recapitulating the complex zonal microarchitecture of native hyaline cartilage,<sup>129</sup> and creating anatomically accurate constructs of stratified cartilage tissues and osteochondral tissue interfaces.<sup>149,150</sup>

Cartilage is a mechanoresponsive tissue, and dynamic stresses play an important role in cartilage development and homeostasis.<sup>151</sup> However, the mechanotransduction pathways, including mechanisms and parameters involved are poorly understood, presenting a major growth area with the potential for discovering new therapeutic approaches in cartilage ageing and disease. Still, advancements for tissue engineering require more reliable assays for the analysis and characterisation of cell behaviour in 3D structures, and for assessing the influence of biomechanical cues on cartilage development. In terms of assessing 3D cartilage-like structures, there is a fundamental need for more reliable assays for *in vitro* assessment and standardisation of protocols, as most available products are specifically made for 2D culture.

### *In silico* modelling of cartilage tissue

To achieve the desired properties of the hydrogels, generally a significant amount of iterations in multi-variant systems is needed for the design, manufacturing and characterisation of these systems.<sup>152</sup> One promising strategy is the emerging concept of rational design that is based on computationally guided biomaterial design strategies.<sup>153</sup> These have been shown to be very suitable when multiple design variables need to be considered. For selecting a biomaterial with suitable mechanical properties, Bas *et al.*<sup>154</sup> developed a numerical model-based approach for the rational design of biomimetic soft network composites to be used in cartilage regeneration. They established a design library capable of predicting the compressive modulus of the designed biomaterials using numerical tools from compressive modulus and Poisson's ratio data of hydrogels found in the literature. This library was

created specifically for soft hydrogels ( $E = \sim 10\text{--}50$  kPa) that can be applied for encapsulating different cells such as human chondrocytes.

Furthermore, a computational model can help to investigate and clarify some of the most significant mechanisms that influence the growth and degradation of the hydrogels used in regenerative medicine. In this regard, an interesting mechanics-based model of tissue growth in degradable cell-laden hydrogels has been reported recently by Sridhar *et al.*<sup>155</sup> In this continuum-based multiphase model, the authors assumed that, after encapsulating cells in a PEG-based hydrogel, hydrolysis of polymer crosslinks was taking place following a first order kinetic law.<sup>156</sup> Then, consequently to the crosslink cleavage, they assumed a release of ECM precursors from the cells to assemble large ECM molecules of aggrecan and collagens. Interestingly, applying their model, they found that well-linked and dense cell agglomerates combined with large areas of weak cross-linking around cells could generate the right conditions/factors for the formation and growth of new tissue while maintaining structural integrity. Similarly, Akalp *et al.*<sup>157</sup> developed a model for interstitial growth, based on mixture theory, which could be used to investigate the influence of cell-laden hydrogel degradation. This was also due to the crosslink cleavage mediated by sensitive enzymes and the transport/diffusion of ECM molecules released by the cells. Upon application to the cartilage tissue, their numerical results showed that the enzymatic degradation produced the presence of a very localized degradation front spreading away from the cells, which could produce immediately a front of growing neo-tissue. Even if these studies utilised real experimental data for the model validation, they did not take in to account the *in vivo* conditions. In this scenario, from a more etiopathological view, Stender *et al.*<sup>158</sup> developed a FE model to study the changes of osteoarthritis-induced articular cartilage damage and the remodelling of subchondral cortical and trabecular bones.

Finally, in spite of the efficiency of the computational models in identifying potential growth mechanisms and supporting the experimental plan, the future models are expected to be able to be used for personalised tissue engineering. This is since the changes in cell behaviour can strongly influence the formation and growth of neo-tissues as well as the dynamic degradation mechanisms of the hydrogels.<sup>159</sup>

### Cell therapies for cartilage regeneration

Degenerative skeletal diseases such as osteoarthritis affect more than 200 million people worldwide. Current strategies of joint replacements lead to the removal of cartilage and healthy bone tissues. Moreover, joint devices and implants have a limited lifespan, requiring revision surgeries within 20 years, so there is a need to move from tissue replacement to tissue regeneration. Matrix autologous chondrocyte implantation (MACI) cell therapies are as expensive as £17 740 (ChondroCelect®, withdrawn from the European Union) per procedure with insufficient evidence of cost-effectiveness.<sup>160</sup> One of the major limitations of MACI is increased timings for patient rehabilitation, caused by poor mechanical and struc-



tural integrity of implanted materials before tissue regeneration.<sup>161</sup> MACI, which was approved in Europe, is also suspended as of 2017.

Autologous chondrocyte implantation (ACI) is available in Europe and the UK (since 2017) for treating symptomatic articular cartilage defects (>2 cm<sup>2</sup>) of the knee.<sup>162</sup> However, ACI is successful for approximately 80% of patients, but for the remaining 20% can produce tissue delamination and hypertrophy of the implantation site.<sup>163</sup> Similarly, a scaffold-free spheroid, Chondrosphere (Spherox), has been approved by the EMA in 2017. Chondrosphere *versus* MACI was £18 000 per quality-adjusted life-year gained.<sup>164</sup> For these cell therapies, new biomimetic hydrogels and materials have the potential to improve the cell therapy outcomes, while decreasing the associated costs. Advanced biomaterials are needed to provide the best environment and support for cartilage cells to function. It is important to note that products containing active biomolecules and/or genes require more complex procedures, regulation, and funding which can limit the sustainability.<sup>13</sup>

In the US market, FDA-approved cell-free hydrogels are Gel-One®, Synvisc and Synvisc-One®.<sup>165,166</sup> In contrast, products that are hydrogel-based with autologous chondrocytes include CaReS®, a type I collagen, and Cartipatch®, which uses an agarose-alginate hydrogel. Cartipatch® has a phase III study terminated and CaRes® is only available in a few selected European countries, Iran, China, and Turkey<sup>167,168</sup>

In summary, this study investigated the mechanical and biological properties of widely used hydrogel materials such as PEG, CS, gelatin, and other materials, for cartilage regeneration. From the literature review, we find that the overall viability of hydrogels based on PEG, CS, or gelatin is high. GAG-based hydrogels namely CS and HA have the highest viability compared to the rest. In general, PEG-based hydrogels have the highest Young's modulus though it is still not adequate compared to the natural articular cartilage compression modulus. Incorporation of additional materials may influence the mechanical properties and viability of chondrocytes. Variation of stiffness and material composition affect chondrocytes to form the matrix. However, research on matrix stiffness and chemistry of hydrogels on cell behaviour is still conflicting. Further research on the effect of stiffness on cellular proliferation, differentiation, ECM production, and migration is needed. Therefore, future studies should focus on investigating the physical, chemical, and biological properties of PEG, CS, and gelatin for use in hydrogels as a scaffold for cartilage regeneration.

## Conflicts of interest

The authors declare no conflicts of interest.

## Acknowledgements

Alexander Stokes acknowledges support from the EPSRC for his Ph.D. studentship (EPSRC Grant EP/R51309X/1).

## References

- H. Huang, H. Xu and J. Zhang, in *Cartilage Tissue Engineering and Regeneration Techniques*, IntechOpen, 2019.
- S. L. Kolasinski, T. Neogi, M. C. Hochberg, C. Oatis, G. Guyatt, J. Block, L. Callahan, C. Copenhaver, C. Dodge and D. Felson, *Arthritis Rheumatol.*, 2020, **72**, 220–233.
- S. L. Vega, M. Y. Kwon and J. A. Burdick, *Eur. Cells Mater.*, 2017, **33**, 59.
- C. W. Archer and P. Francis-West, *Int. J. Biochem. Cell Biol.*, 2003, **35**, 401–404.
- A. J. Sophia Fox, A. Bedi and S. A. Rodeo, *Sports Health*, 2009, **1**, 461–468.
- M. Liu, X. Zeng, C. Ma, H. Yi, Z. Ali, X. Mou, S. Li, Y. Deng and N. He, *Bone Res.*, 2017, **5**, 1–20.
- S. Chen, Y. Falcovitz, R. Schneiderman, A. Maroudas and R. Sah, *Osteoarthr. Cartil.*, 2001, **9**, 561–569.
- D. R. Eyre, *Clin. Orthop. Relat. Res.*, 2004, **427**, S118–S122.
- N. Gudmann and M. Karsdal, in *Biochemistry of Collagens, Laminins and Elastin*, Elsevier, 2016, pp. 73–76.
- Q. Chai, Y. Jiao and X. Yu, *Gels*, 2017, **3**, 6.
- A. J. Sophia Fox, A. Bedi and S. A. Rodeo, *Sports health*, 2009, **1**(6), 461–468.
- F. J. O'brien, *Mater. Today*, 2011, **14**, 88–95.
- D. F. Williams, *Front. Bioeng. Biotechnol.*, 2019, **7**, 127.
- L. Huang, J. Hu, L. Lang, X. Wang, P. Zhang, X. Jing, X. Wang, X. Chen, P. I. Lelkes and A. G. MacDiarmid, *Biomaterials*, 2007, **28**, 1741–1751.
- J. Parsons, in *Handbook of biomaterial properties*, Springer, 1998, pp. 40–47.
- W. Hayes and L. Mockros, *J. Appl. Physiol.*, 1971, **31**, 562–568.
- S. Akizuki, V. C. Mow, F. Müller, J. C. Pita, D. S. Howell and D. H. Manicourt, *J. Orthop. Res.*, 1986, **4**, 379–392.
- F. Couet, N. Rajan and D. Mantovani, *Macromol. Biosci.*, 2007, **7**, 701–718.
- B. Marelli, M. Achilli, A. Alessandrino, G. Freddi, M. C. Tanzi, S. Farè and D. Mantovani, *Macromol. Biosci.*, 2012, **12**, 1566–1574.
- D. Pankajakshan and D. K. Agrawal, *Can. J. Physiol. Pharmacol.*, 2010, **88**, 855–873.
- M. Achilli, J. Lagueux and D. Mantovani, *Macromol. Biosci.*, 2010, **10**, 307–316.
- A. M. Ferreira, P. Gentile, S. Sartori, C. Pagliano, C. Cabrele, V. Chiono and G. Ciardelli, *Biotechnol. J.*, 2012, **7**, 1386–1394.
- D. A. Gyles, L. D. Castro, J. O. C. Silva Jr. and R. M. Ribeiro-Costa, *Eur. Polym. J.*, 2017, **88**, 373–392.
- N. J. Einerson, K. R. Stevens and W. J. Kao, *Biomaterials*, 2003, **24**, 509–523.
- S. Kapoor and S. C. Kundu, *Acta Biomater.*, 2016, **31**, 17–32.
- M. J. Rodriguez, J. Brown, J. Giordano, S. J. Lin, F. G. Omenetto and D. L. Kaplan, *Biomaterials*, 2017, **117**, 105–115.
- M. Kumar, P. Gupta, S. Bhattacharjee, S. K. Nandi and B. B. Mandal, *Biomaterials*, 2018, **187**, 1–17.



- 28 A. Armiento, M. Stoddart, M. Alini and D. Eglin, *Acta Biomater.*, 2018, **65**, 1–20.
- 29 L. Lapčák, L. Lapcik, S. De Smedt, J. Demeester and P. Chabreck, *Chem. Rev.*, 1998, **98**, 2663–2684.
- 30 R. L. Jackson, S. J. Busch and A. D. Cardin, *Physiol. Rev.*, 1991, **71**, 481–539.
- 31 J. Baier Leach, K. A. Bivens, C. W. Patrick Jr. and C. E. Schmidt, *Biotechnol. Bioeng.*, 2003, **82**, 578–589.
- 32 A. Scalzone, M. A. Bonifacio, S. Cometa, F. Cucinotta, E. De Giglio, A. M. Ferreira and P. Gentile, *Front. Bioeng. Biotechnol.*, 2020, **8**, 712.
- 33 P. Rastogi and B. Kandasubramanian, *Biofabrication*, 2019, **11**, 042001.
- 34 A. D. Augst, H. J. Kong and D. J. Mooney, *Macromol. Biosci.*, 2006, **6**, 623–633.
- 35 P. Gentile, C. Ghione, A. Ferreira, A. Crawford and P. Hatton, *Biomater. Sci.*, 2017, **5**, 1922–1931.
- 36 S. Peers, A. Montebault and C. Ladavière, *J. Controlled Release*, 2020, **326**, 150–163.
- 37 Y. Xie, X. Liao, J. Zhang, F. Yang and Z. Fan, *Int. J. Biol. Macromol.*, 2018, **119**, 402–412.
- 38 K. E. Benders, P. R. van Weeren, S. F. Badylak, D. B. Saris, W. J. Dhert and J. Malda, *Trends Biotechnol.*, 2013, **31**, 169–176.
- 39 C.-C. Lin and K. S. Anseth, *Pharm. Res.*, 2009, **26**, 631–643.
- 40 J. Zhu, *Biomaterials*, 2010, **31**, 4639–4656.
- 41 Z. Fan, P. Cheng, M. Liu, D. Li, G. Liu, Y. Zhao, Z. Ding, F. Chen, B. Wang and X. Tan, *New J. Chem.*, 2017, **41**, 8656–8662.
- 42 B. Liu, W. Huang, G. Yang, Y. An, Y. Yin, N. Wang and B. Jiang, *Mater. Sci. Eng., C*, 2020, **116**, 111259.
- 43 S. P. Higgins, A. K. Solan and L. E. Niklason, *J. Biomed. Mater. Res., Part A*, 2003, **67**, 295–302.
- 44 H. Liu, E. B. Slamovich and T. J. Webster, *Int. J. Nanomed.*, 2006, **1**, 541.
- 45 S. A. Munim and Z. A. Raza, *J. Porous Mater.*, 2019, **26**, 881–901.
- 46 B. Gupta, N. Revagade and J. Hilborn, *Prog. Polym. Sci.*, 2007, **32**, 455–482.
- 47 B. Dhandayuthapani, Y. Yoshida, T. Maekawa and D. S. Kumar, *Int. J. Polym. Sci.*, 2011, **2011**, 290602.
- 48 A. Kosik-Kozioł, M. Costantini, T. Bolek, K. Szöke, A. Barbetta, J. Brinckmann and W. Świążkowski, *Biofabrication*, 2017, **9**, 044105.
- 49 A. Basu, K. R. Kunduru, S. Doppalapudi, A. J. Domb and W. Khan, *Adv. Drug Delivery Rev.*, 2016, **107**, 192–205.
- 50 W. Bao, M. Li, Y. Yang, Y. Wan, X. Wang, N. Bi and C. Li, *Front. Chem.*, 2020, **8**, 53.
- 51 M. C. Catoira, L. Fusaro, D. Di Francesco, M. Ramella and F. Boccafroschi, *J. Mater. Sci. Mater. Med.*, 2019, **30**, 115.
- 52 B. Johnstone, M. Alini, M. Cucchiaroni, G. R. Dodge, D. Eglin, F. Guilak, H. Madry, A. Mata, R. L. Mauck and C. E. Semino, *Eur. Cells Mater.*, 2013, **25**(248), e67.
- 53 L. Han, M. Wang, P. Li, D. Gan, L. Yan, J. Xu, K. Wang, L. Fang, C. W. Chan and H. Zhang, *ACS Appl. Mater. Interfaces*, 2018, **10**, 28015–28026.
- 54 J. Kim, C. Lee and J. H. Ryu, *Appl. Sci.*, 2021, **11**, 21.
- 55 K. R. Hixon, S. J. Bogner, G. Ronning-Arnesen, B. E. Janowiak and S. A. Sell, *Gels*, 2019, **5**, 21.
- 56 M. A. Bonifacio, S. Cometa, A. Cochis, P. Gentile, A. M. Ferreira, B. Azzimonti, G. Procino, E. Ceci, L. Rimondini and E. De Giglio, *Carbohydr. Polym.*, 2018, **198**, 462–472.
- 57 H. Fan and J. P. Gong, *Macromolecules*, 2020, **53**, 2769–2782.
- 58 W. He, M. Reaume, M. Hennenfent, B. P. Lee and R. Rajachar, *Biomater. Sci.*, 2020, **8**(12), 3248–3269.
- 59 X. Xu, V. V. Jerca and R. Hoogenboom, *Mater. Horiz.*, 2021, DOI: 10.1039/D0MH01514H.
- 60 S. Khan and N. M. Ranjha, *Polym. Bull.*, 2014, **71**, 2133–2158.
- 61 W. Hu, Z. Wang, Y. Xiao, S. Zhang and J. Wang, *Biomater. Sci.*, 2019, **7**, 843–855.
- 62 Y. H. Tan, J. R. Schallom, N. V. Ganesh, K. Fujikawa, A. V. Demchenko and K. J. Stine, *Nanoscale*, 2011, **3**(8), 3395–3407.
- 63 J. Wu, Q. Chen, C. Deng, B. Xu, Z. Zhang, Y. Yang and T. Lu, *Theranostics*, 2020, **10**, 9843.
- 64 S. H. Park, J. Y. Seo, J. Y. Park, Y. B. Ji, K. Kim, H. S. Choi, S. Choi, J. H. Kim, B. H. Min and M. S. Kim, *NPG Asia Mater.*, 2019, **11**, 1–16.
- 65 P. Nezhad-Mokhtari, M. Ghorbani, L. Roshangar and J. S. Rad, *Int. J. Biol. Macromol.*, 2019, **139**, 760–772.
- 66 C. Echaliier, L. Valot, J. Martinez, A. Mehdi and G. Subra, *Mater. Today Commun.*, 2019, **20**, 100536.
- 67 Y. Zhang, Y. Cao, H. Zhao, L. Zhang, T. Ni, Y. Liu, Z. An, M. Liu and R. Pei, *J. Mater. Chem. B*, 2020, **8**, 4237–4244.
- 68 C.-C. Tsai, S.-H. Kuo, T.-Y. Lu, N.-C. Cheng, M.-Y. Shie and J. Yu, *ACS Biomater. Sci. Eng.*, 2020, **6**, 5110–5119.
- 69 R. Parhi, *Adv. Pharm. Bull.*, 2017, **7**, 515–530.
- 70 G. C. Ingavle, N. H. Dormer, S. H. Gehrke and M. S. Detamore, *J. Mater. Sci. Mater. Med.*, 2012, **23**, 157–170.
- 71 E. S. Dragan, *Chem. Eng. J.*, 2014, **243**, 572–590.
- 72 E. S. Dragan, *Pure Appl. Chem.*, 2014, **86**, 1707–1721.
- 73 T. Nonoyama and J. P. Gong, *Proc. Inst. Mech. Eng., Part H*, 2015, **229**, 853–863.
- 74 Y. Zhao, T. Nakajima, J. J. Yang, T. Kurokawa, J. Liu, J. Lu, S. Mizumoto, K. Sugahara, N. Kitamura and K. Yasuda, *Adv. Mater.*, 2014, **26**, 436–442.
- 75 L. Li, K. Zhang, T. Wang, P. Wang, B. Xue, Y. Cao, L. Zhu and Q. Jiang, *Mater. Des.*, 2020, **189**, 108492.
- 76 A. K. Means, C. S. Shrode, L. V. Whitney, D. A. Ehrhardt and M. A. Grunlan, *Biomacromolecules*, 2019, **20**, 2034–2042.
- 77 B. G. Cooper, R. C. Stewart, D. Burstein, B. D. Snyder and M. W. Grinstaff, *Angew. Chem.*, 2016, **128**, 4298–4302.
- 78 L. Trachsel, C. Johnbosco, T. Lang, E. M. Benetti and M. Zenobi-Wong, *Biomacromolecules*, 2019, **20**, 4502–4511.
- 79 J. A. Buckwalter and E. B. Hunziker, *Lancet*, 1996, **348**, S18.
- 80 A. B. Bello, D. Kim, D. Kim, H. Park and S.-H. Lee, *Tissue Eng., Part B*, 2020, **26**, 164–180.





- 81 S. M. Ryan, G. Mantovani, X. Wang, D. M. Haddleton and D. J. Brayden, *Expert Opin. Drug Delivery*, 2008, **5**, 371–383.
- 82 Y. Alinejad, A. Adoungotchodo, E. Hui, F. Zehtabi and S. Lerouge, *Int. J. Biol. Macromol.*, 2018, **113**, 132–141.
- 83 N. Kuiper and A. Sharma, *Osteoarthr. Cartil.*, 2015, **23**, 2233–2241.
- 84 J. Roberts and P. Martens, in *Biosynthetic Polymers for Medical Applications*, Elsevier, 2016, pp. 205–239.
- 85 D.-A. Wang, S. Varghese, B. Sharma, I. Strehin, S. Fermanian, J. Gorham, D. H. Fairbrother, B. Cascio and J. H. Elisseeff, *Nat. Mater.*, 2007, **6**, 385–392.
- 86 E. C. Collin, O. Carroll, M. Kilcoyne, M. Peroglio, E. See, D. Hendig, M. Alini, S. Grad and A. Pandit, *Signal Transduction Targeted Ther.*, 2017, **2**, 1–8.
- 87 T. Wang and F. Yang, *Stem Cell Res. Ther.*, 2017, **8**, 1–12.
- 88 L. Zhou, L. Fan, F.-M. Zhang, Y. Jiang, M. Cai, C. Dai, Y.-A. Luo, L.-J. Tu, Z.-N. Zhou and X.-J. Li, *Bioact. Mater.*, 2020, **6**, 890–904.
- 89 X. Bai, S. Lü, Z. Cao, B. Ni, X. Wang, P. Ning, D. Ma, H. Wei and M. Liu, *Carbohydr. Polym.*, 2017, **166**, 123–130.
- 90 F. Chen, S. Yu, B. Liu, Y. Ni, C. Yu, Y. Su, X. Zhu, X. Yu, Y. Zhou and D. Yan, *Sci. Rep.*, 2016, **6**, 20014.
- 91 T. Li, X. Song, C. Weng, X. Wang, L. Sun, X. Gong, L. Yang and C. Chen, *Appl. Mater. Today*, 2018, **10**, 173–183.
- 92 N. S. Hwang, S. Varghese, H. J. Lee, P. Theprungsirikul, A. Canver, B. Sharma and J. Elisseeff, *FEBS Lett.*, 2007, **581**, 4172–4178.
- 93 Z. Zhu, Y. M. Wang, J. Yang and X. S. Luo, *Plast. Aesthet. Res.*, 2017, **4**, 219–227.
- 94 S. Van Vlierberghe, G.-J. Graulus, S. K. Samal, I. Van Nieuwenhove and P. Dubruel, *Biomedical Foams for Tissue Engineering Applications*, Elsevier, 2014, pp. 335–390.
- 95 Z. Muñoz, H. Shih and C.-C. Lin, *Biomater. Sci.*, 2014, **2**, 1063–1072.
- 96 P. Jaipan, A. Nguyen and R. J. Narayan, *MRS Commun.*, 2017, **7**, 416–426.
- 97 B. F. Pierce, E. Pittermann, N. Ma, T. Gebauer, A. T. Neffe, M. Hölscher, F. Jung and A. Lendlein, *Macromol. Biosci.*, 2012, **12**, 312–321.
- 98 S. Pahoff, C. Meinert, O. Bas, L. Nguyen, T. J. Klein and D. W. Huttmacher, *J. Mater. Chem. B*, 2019, **7**, 1761–1772.
- 99 Y. Xu, J. Peng, G. Richards, S. Lu and D. Eglin, *J. Orthop. Translat.*, 2019, **18**, 128–141.
- 100 K. R. Stevens, J. S. Miller, B. L. Blakely, C. S. Chen and S. N. Bhatia, *J. Biomed. Mater. Res., Part A*, 2015, **103**, 3331–3338.
- 101 C. D. Spicer, *Polym. Chem.*, 2020, **11**, 184–219.
- 102 C. Fiedler, E. Aisenbrey, J. Wahlquist, C. Heveran, V. Ferguson, S. Bryant and R. McLeod, *Soft Matter*, 2016, **12**, 9095–9104.
- 103 S. J. Bryant and K. S. Anseth, *J. Biomed. Mater. Res., Part A*, 2003, **64**, 70–79.
- 104 Y. D. Taghipour, V. R. Hokmabad, D. Bakhshayesh, A. Rahmani, N. Asadi, R. Salehi and H. T. Nasrabadi, *Curr. Med. Chem.*, 2020, **27**(16), 2658–2680.
- 105 A. Kerin, M. Wisnom and M. Adams, *Proc. Inst. Mech. Eng., Part H*, 1998, **212**, 273–280.
- 106 C. Tang, B. D. Holt, Z. M. Wright, A. M. Arnold, A. C. Moy and S. A. Sydlik, *J. Mater. Chem. B*, 2019, **7**, 2442–2453.
- 107 W. Schuurman, P. A. Levett, M. W. Pot, P. R. van Weeren, W. J. Dhert, D. W. Huttmacher, F. P. Melchels, T. J. Klein and J. Malda, *Macromol. Biosci.*, 2013, **13**, 551–561.
- 108 P. Smeriglio, J. H. Lai, F. Yang and N. Bhutani, *J. Visualized Exp.*, 2015, **104**, e53085.
- 109 D. Zhu, P. Trinh, E. Liu and F. Yang, *ACS Biomater. Sci. Eng.*, 2018, **4**, 3561–3569.
- 110 L. H. Nguyen, A. K. Kudva, N. S. Saxena and K. Roy, *Biomaterials*, 2011, **32**, 6946–6952.
- 111 I. Strehin, Z. Nahas, K. Arora, T. Nguyen and J. Elisseeff, *Biomaterials*, 2010, **31**, 2788–2797.
- 112 S. Varghese, N. S. Hwang, A. C. Canver, P. Theprungsirikul, D. W. Lin and J. Elisseeff, *Matrix Biol.*, 2008, **27**, 12–21.
- 113 X. Zhao, A. Papadopoulos, S. Ibusuki, D. A. Bichara, D. B. Saris, J. Malda, K. S. Anseth, T. J. Gill and M. A. Randolph, *BMC Musculoskeletal Disord.*, 2016, **17**, 245.
- 114 F. Yu, X. Cao, Y. Li, L. Zeng, B. Yuan and X. Chen, *Polym. Chem.*, 2013, **5**, 1082–1090.
- 115 G. Gao, A. F. Schilling, K. Hubbell, T. Yonezawa, D. Truong, Y. Hong, G. Dai and X. Cui, *Biotechnol. Lett.*, 2015, **37**, 2349–2355.
- 116 S. Bang, U.-W. Jung and I. Noh, *Tissue Eng. Regener. Med.*, 2018, **15**, 25–35.
- 117 C. Gegg and F. Yang, *Acta Biomater.*, 2020, **101**, 196–205.
- 118 H. Lin, A. M. Beck, K. Shimomura, J. Sohn, M. R. Fritch, Y. Deng, E. J. Kilroy, Y. Tang, P. G. Alexander and R. S. Tuan, *J. Tissue Eng. Regener. Med.*, 2019, **13**, 1418–1429.
- 119 Y. Xu, Z. Wang, Y. Hua, X. Zhu, Y. Wang, L. Duan, L. Zhu, G. Jiang, H. Xia and Y. She, *Mater. Sci. Eng., C*, 2020, 111628.
- 120 V. Moulisová, S. Poveda-Reyes, E. Sanmartín-Masiá, L. Quintanilla-Sierra, M. Salmerón-Sánchez and G. Gallego Ferrer, *ACS Omega*, 2017, **2**, 7609–7620.
- 121 X. Jiang, J. Liu, Q. Liu, Z. Lu, L. Zheng, J. Zhao and X. Zhang, *Biomater. Sci.*, 2018, **6**, 1616–1626.
- 122 L. Zhang, K. Li, W. Xiao, L. Zheng, Y. Xiao, H. Fan and X. Zhang, *Carbohydr. Polym.*, 2011, **84**, 118–125.
- 123 F. Yu, X. Cao, L. Zeng, Q. Zhang and X. Chen, *Carbohydr. Polym.*, 2013, **97**, 188–195.
- 124 X. Hu, D. Li, F. Zhou and C. Gao, *Acta Biomater.*, 2011, **7**, 1618–1626.
- 125 P. A. Levett, F. P. Melchels, K. Schrobback, D. W. Huttmacher, J. Malda and T. J. Klein, *Acta Biomater.*, 2014, **10**, 214–223.
- 126 A. Vedadghavami, F. Minooei, M. H. Mohammadi, S. Khetani, A. R. Kolahchi, S. Mashayekhan and A. Sanati-Nezhad, *Acta Biomater.*, 2017, **62**, 42–63.
- 127 M. W. Tibbitt and K. S. Anseth, *Biotechnol. Bioeng.*, 2009, **103**, 655–663.
- 128 Q. T. Nguyen, Y. Hwang, A. C. Chen, S. Varghese and R. L. Sah, *Biomaterials*, 2012, **33**, 6682–6690.



- 129 J.-H. Kim, G. Lee, Y. Won, M. Lee, J.-S. Kwak, C.-H. Chun and J.-S. Chun, *Proc. Natl. Acad. Sci. U. S. A.*, 2015, **112**, 9424–9429.
- 130 B. V. Sridhar, J. L. Brock, J. S. Silver, J. L. Leight, M. A. Randolph and K. S. Anseth, *Adv. Healthcare Mater.*, 2015, **4**, 702–713.
- 131 D. L. Butler, S. A. Goldstein and F. Guilak, *J. Biomech. Eng.*, 2000, **122**, 570–575.
- 132 S. Pettersson, J. Wetterö, P. Tengvall and G. Kratz, *J. Tissue Eng. Regener. Med.*, 2009, **3**, 450–460.
- 133 J. Samuelsen, H. Kopperud, J. Holme, I. Dragland, T. Christensen and J. Dahl, *J. Biomed. Mater. Res., Part A*, 2011, **96**, 395–401.
- 134 H. Schweikl, G. Spagnuolo and G. Schmalz, *J. Dent. Res.*, 2006, **85**, 870–877.
- 135 P. D. Drumheller and J. A. Hubbell, *J. Biomed. Mater. Res.*, 1995, **29**, 207–215.
- 136 E. Tziampazis, J. Kohn and P. V. Moghe, *Biomaterials*, 2000, **21**, 511–520.
- 137 C.-S. Ko, J.-P. Huang, C.-W. Huang and I.-M. Chu, *J. Biosci. Bioeng.*, 2009, **107**, 177–182.
- 138 J. A. Iocono, T. M. Krummel, K. A. Keefer, G. M. Allison and H. P. Ehrlich, *Wound Repair Regen.*, 1998, **6**, 442–448.
- 139 S. J. Bryant, K. S. Anseth, D. A. Lee and D. L. Bader, *J. Orthop. Res.*, 2004, **22**, 1143–1149.
- 140 B. Balakrishnan and R. Banerjee, *Chem. Rev.*, 2011, **111**, 4453–4474.
- 141 S.-H. Lee and H. Shin, *Adv. Drug Delivery Rev.*, 2007, **59**, 339–359.
- 142 E.-Y. Chuang, C.-W. Chiang, P.-C. Wong and C.-H. Chen, *Adv. Mater. Sci. Eng.*, 2018, **2018**, 4368910.
- 143 L. Fu, Z. Yang, C. Gao, H. Li, Z. Yuan, F. Wang, X. Sui, S. Liu and Q. Guo, *Regener. Biomater.*, 2020, **7**(6), 527–542.
- 144 R. Longley, A. M. Ferreira and P. Gentile, *Int. J. Mol. Sci.*, 2018, **19**, 1755.
- 145 D. Gan, Z. Wang, C. Xie, X. Wang, W. Xing, X. Ge, H. Yuan, K. Wang, H. Tan and X. Lu, *Adv. Healthcare Mater.*, 2019, **8**, 1901103.
- 146 J. Liao, T. Tian, S. Shi, X. Xie, Q. Ma, G. Li and Y. Lin, *Bone Res.*, 2017, **5**, 1–15.
- 147 H. Xia, D. Zhao, H. Zhu, Y. Hua, K. Xiao, Y. Xu, Y. Liu, W. Chen, Y. Liu and W. Zhang, *ACS Appl. Mater. Interfaces*, 2018, **10**, 31704–31715.
- 148 J. Xiongfa, Z. Hao, Z. Liming and X. Jun, *Regener. Med.*, 2018, **13**, 73–87.
- 149 A. C. Daly, F. E. Freeman, T. Gonzalez-Fernandez, S. E. Critchley, J. Nulty and D. J. Kelly, *Adv. Healthcare Mater.*, 2017, **6**, 1700298.
- 150 Y. Wu, P. Kennedy, N. Bonazza, Y. Yu, A. Dhawan and I. Ozbolat, *Cartilage*, 2018, 1947603518809410.
- 151 Z. Zhao, Y. Li, M. Wang, S. Zhao, Z. Zhao and J. Fang, *J. Cell. Mol. Med.*, 2020, **24**, 5408–5419.
- 152 G. Hautier, A. Jain and S. P. Ong, *J. Mater. Sci.*, 2012, **47**, 7317–7340.
- 153 A. A. Zadpoor, *J. Mech. Behav. Biomed. Mater.*, 2017, **70**, 1–6.
- 154 O. Bas, S. Lucarotti, D. D. Angella, N. J. Castro, C. Meinert, F. M. Wunner, E. Rank, G. Vozzi, T. J. Klein and I. Catelas, *Chem. Eng. J.*, 2018, **340**, 15–23.
- 155 S. L. Sridhar, M. C. Schneider, S. Chu, G. De Roucy, S. J. Bryant and F. J. Vernerey, *Soft Matter*, 2017, **13**, 4841–4855.
- 156 A. T. Metters, C. N. Bowman and K. S. Anseth, *J. Phys. Chem. B*, 2000, **104**, 7043–7049.
- 157 U. Akalp, S. J. Bryant and F. J. Vernerey, *Soft Matter*, 2016, **12**, 7505–7520.
- 158 M. E. Stender, R. D. Carpenter, R. A. Regueiro and V. L. Ferguson, *J. Biomech.*, 2016, **49**, 3502–3508.
- 159 S. J. Bryant and F. J. Vernerey, *Adv. Healthcare Mater.*, 2018, **7**, 1700605.
- 160 E. Hanna, C. Rémuzat, P. Auquier and M. Toumi, *Value Health*, 2016, **19**, A487.
- 161 P. C. Kreuz, R. H. Kalkreuth, P. Niemeyer, M. Uhl and C. Erggelet, *Cartilage*, 2019, **10**, 305–313.
- 162 X. Armoiry, E. Cummins, M. Connock, A. Metcalfe, P. Royle, R. Johnston, J. Rodrigues, N. Waugh and H. Mistry, *PharmacoEconomics*, 2019, **37**, 879–886.
- 163 W. Zhang, H. Ouyang, C. R. Dass and J. Xu, *Bone Res.*, 2016, **4**, 1–14.
- 164 H. Mistry, M. Connock, J. Pink, D. Shyangdan, C. Clar, P. Royle, R. Court, L. C. Biant, A. Metcalfe and N. Waugh, *Health Technol. Assess.*, 2017, **21**(6), DOI: 10.3310/hta21060.
- 165 J. Takamura, T. Seo and V. Strand, *Cartilage*, 2019, **10**, 417–422.
- 166 O. De Lucia, J. Jerosch, S. Yoon, T. Sayre, W. Ngai and G. Filippou, *Clin. Rheumatol.*, 2020, 1–10.
- 167 A. Clavé, J. F. Potel, E. Servien, P. Neyret, F. Dubrana and E. Stindel, *J. Orthop. Res.*, 2016, **34**, 658–665.
- 168 B. J. Huang, J. C. Hu and K. A. Athanasiou, *Biomaterials*, 2016, **98**, 1–22.

