

CrossMark
click for updatesCite this: *Chem. Sci.*, 2016, 7, 3399

Heteronanowires of MoC–Mo₂C as efficient electrocatalysts for hydrogen evolution reaction†

Huanlei Lin,^a Zhangping Shi,^b Sina He,^a Xiang Yu,^{ac} Sinong Wang,^b Qingsheng Gao^{*a} and Yi Tang^{*b}

Exploring efficient noble-metal free electrocatalysts for the hydrogen evolution reaction (HER) is one of the most promising pathways for facing the energy crisis. Herein, MoC–Mo₂C heteronanowires composed of well-defined nanoparticles were accomplished *via* controlled carbonization, showing excellent HER activity, fast kinetic metrics and outstanding stability in both acid and basic electrolytes. In particular, the optimal one consisting of 31.4 wt% MoC displayed a low overpotential ($\eta_{10} = 126$ and 120 mV for reaching a current density of -10 mA cm^{-2}), a small Tafel slope (43 and 42 mV dec⁻¹) and a low onset overpotential (38 and 33 mV) in 0.5 M H₂SO₄ and 1.0 M KOH, respectively. Such prominent performance, outperforming most of the current noble-metal free electrocatalysts, was ascribed to the carbide surface with an optimized electron density, and the consequently facilitated HER kinetics. This work elucidates a feasible way toward efficient electrocatalysts *via* heteronanostructure engineering, shedding some light on the exploration and optimization of catalysts in energy chemistry.

Received 7th January 2016
Accepted 11th February 2016

DOI: 10.1039/c6sc00077k

www.rsc.org/chemicalscience

Introduction

The rapid growth of global energy consumption and the associated environmental issues have triggered an urgent demand for renewable and clean energy sources.^{1,2} Hydrogen (H₂) is a promising candidate as it stores energy from renewable sources (*e.g.*, sunlight and wind) into the chemical bond *via* the electrolysis of water, which then can be released through the reverse reaction in fuel cells on demand.³ The hydrogen evolution reaction (HER) *via* water electrolysis essentially depends on the efficiency of electrocatalysts, which must be stable and capable of reducing water rapidly at potentials close to its thermodynamic value.^{4,5} Although noble metals, *e.g.*, platinum, show high activity, they are severely limited by their high cost and low abundance.^{6,7} It is urgently demanded to develop noble-metal free catalysts with good activity, long-term stability, high element-abundance, and economical cost.^{5,8–10}

Remarkable advances have been recently made regarding the use of transition-metals and their carbides, nitrides,

chalcogenides and phosphides.^{5,8,10,11} Presenting varied electronic features and catalytic properties related to tunable phases and composition,^{12–15} molybdenum carbides (MoC_x) have received special attention as one of the promising noble-metal free catalysts. Among them, Mo₂C demonstrates the best performance because of its electron configuration around the Fermi level (E_F).^{13,16} Intense effort has been devoted to Mo₂C nanostructures with enriched active-sites,^{17–26} and composites integrating a conducting matrix, *e.g.*, carbon nanotubes (CNTs) and graphene (GR).^{27–31} However, the negative hydrogen-binding energy (ΔG_{H^*}) on Mo₂C indicates a strong adsorption of H on the Mo₂C surface, which benefits H⁺ reduction (*i.e.*, Volmer step), but restricts H_{ads} desorption (*i.e.*, the Heyrovsky/Tafel step).^{16,32} Thus, an optimization of the electronic features are desired. The introduction of doping elements has even been employed,^{33,34} *via* which the improvement is however limited due to inadequate modification and inevitable structure damage. It is notable that the electron density around the Mo active-sites mostly relies on the carbon in the lattice,^{35,36} which will be reduced with increasing C because of the electron-transfer from Mo to C.¹⁴ For example, with a high C content, MoC usually presents weaker hydrogen binding in comparison with that on Mo₂C, and consequently a facilitated Heyrovsky/Tafel step, but a hindered Volmer reaction.^{13,29} Regarding the respectively promoted elementary reactions of HER on Mo₂C and MoC, it's promising to achieve a synergistically-enhanced activity on MoC–Mo₂C interfaces, which are rarely reported to the best of our knowledge.

Herein, we report novel MoC–Mo₂C heteronanowires (HNWs) as efficient HER electrocatalysts, which are fabricated

^aDepartment of Chemistry, Jinan University, Guangzhou 510632, China. E-mail: tqsgao@jnu.edu.cn

^bDepartment of Chemistry, Shanghai Key Laboratory of Molecular Catalysis and Innovative Materials, Laboratory of Advanced Materials and Collaborative Innovation Center of Chemistry for Energy Materials, Fudan University, Shanghai 200433, China. E-mail: yitang@fudan.edu.cn

^cAnalytic and Testing Centre, Jinan University, Guangzhou 510632, China

† Electronic supplementary information (ESI) available: SEM, XRD, FT-IR, TG/DSC and CHN elemental analysis of hybrid precursors, additional XPS results, SEM, TEM, N₂-sorption isothermals, Raman spectra, CV and EIS of a series of MoC_x and their comparison with previously reported noble-metal free catalysts. See DOI: 10.1039/c6sc00077k



from MoO_x -amine nanowires (NWs) *via* controlled carbonization. The HNWs denoted as $\text{MoC-Mo}_2\text{C-}n$ (where n refers to the MoC weight percentage) are one-dimensional (1D) heterostructures composed of defined nanoparticles (NPs), with rich nanoporosity, large surface area, and more importantly a tunable composition. This is remarkably improved from our previous work on nanoporous Mo_2C ,²¹ highlighted by the effective electron regulation and further improved activity *via* varying MoC/ Mo_2C in the HNWs. With an optimal composition, $\text{MoC-Mo}_2\text{C-31.4}$ exhibits a low η_{10} (overpotential required to reach a current density of -10 mA cm^{-2}) of 126 mV, a low Tafel slope of 43 mV dec^{-1} , and a low η_{onset} (overpotential referring to the beginning of the linear regime in the Tafel plot) of 38 mV in $0.5 \text{ M H}_2\text{SO}_4$, outperforming most of the current noble-metal free electrocatalysts. The high HER activity should be ascribed to the moderated electron density on the carbide surface, which optimizes the hydrogen-binding and thus the HER kinetics. In addition, the good efficiency in basic electrolyte further verifies $\text{MoC-Mo}_2\text{C}$ HNWs as promising noble-metal free electrocatalysts.

Results and discussion

As shown in Fig. 1a, a series of MoC_x HNWs can be achieved *via* the controlled carbonization of various MoO_x -amine precursors (Table S1[†]), which were firstly fabricated through reacting molybdate with aniline (An) or *p*-methylaniline (MeAn). The wire-like precursors (Fig. S1[†]) obtained with An at pH 4.0 (MoAn-4.0) and 3.5 (MoAn-3.5) were respectively confirmed as $\text{Mo}_3\text{O}_{10}(\text{C}_6\text{H}_8\text{N})_2 \cdot 2\text{H}_2\text{O}$ (JCPDS no. 50-2402) and its mixture with $\text{Mo}_8\text{O}_{25}(\text{C}_6\text{H}_8\text{N})_2 \cdot 2\text{H}_2\text{O}$ (JCPDS no. 49-2068), using X-ray diffraction (XRD, Fig. S2[†]). For those obtained with MeAn (MoMeAn-4.0), a similar XRD pattern with an obvious shift to lower degree values suggests an analogous crystalline structure with an expanded lattice due to the large MeAn molecule. Their

composition was further evidenced using Fourier transform infrared (FT-IR), thermogravimetric analysis coupled with differential scanning calorimetry (TGA/DSC), and CHN elemental analysis (Fig. S3[†]). Obviously, the different carbon content will benefit the controlled synthesis of MoC_x .³⁷

The XRD investigation clearly confirms the achievement of various MoC_x (Fig. 1b), whose composition was further determined through the combined measurements of XRD, CHN elemental analysis and inductively coupled plasma (ICP) (Table S2[†]). The product α - Mo_2C (JCPDS no. 31-0871) was obtained from calcining MoAn-3.5 at $775 \text{ }^\circ\text{C}$, and η -MoC (JCPDS no. 08-0384) was obtained from MoMeAn-4.0 at $700 \text{ }^\circ\text{C}$. The heterostructures of $\text{MoC-Mo}_2\text{C-31.4}$ and $\text{MoC-Mo}_2\text{C-68.1}$ were harvested from MoAn-4.0 and MoMeAn-4.0, respectively, at $775 \text{ }^\circ\text{C}$. As expected, the carbon source in the hybrid precursors contributes to the tailored generation of carbides. The higher carbon content of MoAn-4.0 (22.9%) compared to that of MoAn-3.5 (20.7%) benefits the formation of some MoC in Mo_2C , and having sufficient carbon (25.3%) in MoMeAn-4.0 leads to the pure phase of MoC.

These samples were further analyzed using X-ray photoelectron spectroscopy (XPS, Fig. 1c). The peak fitting of Mo 3d profiles suggests that there are four states (+2, +3, +4 and +6) for Mo on the surface.^{17,38} The Mo^{4+} and Mo^{6+} species result from the inactive MoO_2 and MoO_3 , respectively, which are commonly observed as carbides are exposed to air.³⁹ We focus on the Mo^{2+} and Mo^{3+} species with peaks at $228.0\text{--}229.0 \text{ eV}$ ($\text{Mo } 3d_{5/2}$) and $231.0\text{--}232.0 \text{ eV}$ ($\text{Mo } 3d_{3/2}$), because they are the active centres for electrocatalytic HER.^{13,17} The $\text{Mo}^{3+}/\text{Mo}^{2+}$ mole ratios ($n_{3+/2+}$) on the MoC_x surface can provide useful information to understand the nature of the active-sites (Table S3[†]). The $n_{3+/2+}$ values for Mo_2C and MoC are 0.4 and 10.9 (Fig. 1c), respectively, which suggests that Mo^{2+} is dominant to Mo^{3+} on Mo_2C , while Mo^{3+} is prevailing on MoC. In the heterostructures, $n_{3+/2+}$ visibly changed to 3.0 for $\text{MoC-Mo}_2\text{C-31.4}$, and 7.2 for $\text{MoC-Mo}_2\text{C-68.1}$. Such a variation of $\text{Mo}^{3+}/\text{Mo}^{2+}$ will influence the HER activity, related to the different electron density around Mo^{3+} and Mo^{2+} .¹³

Meanwhile, the Raman spectra of the above MoC_x samples display the D- and G-bands of carbon at 1350 and 1590 cm^{-1} , respectively, confirming the presence of free carbon (Fig. S4[†]).²⁵ In addition, N_2 isothermal sorption reveals the large surface of the MoC_x NWs (Fig. S5[†]). Particularly, $\text{MoC-Mo}_2\text{C-31.4}$ HNWs present a specific surface area of $58.5 \text{ m}^2 \text{ g}^{-1}$, larger than that of Mo_2C ($39.3 \text{ m}^2 \text{ g}^{-1}$), $\text{MoC-Mo}_2\text{C-68.1}$ ($33.7 \text{ m}^2 \text{ g}^{-1}$) and MoC ($26.0 \text{ m}^2 \text{ g}^{-1}$). A major pore distribution at around 5.5 nm is observed for Mo_2C and $\text{MoC-Mo}_2\text{C-31.4}$.

Taking $\text{MoC-Mo}_2\text{C-31.4}$ as the model sample, the heterostructures can be well confirmed using scanning electron microscopy (SEM) and transmission electron microscopy (TEM). Wire-like products several micrometres in length and $80\text{--}150 \text{ nm}$ in width are observed in Fig. 2a, maintaining the 1D morphology of the precursors. TEM further displays that such NWs are composed of NPs ($\sim 10 \text{ nm}$), and the selected area electron diffraction (SAED) pattern corresponds to those of α - Mo_2C and η -MoC (Fig. 2b). Accordingly, the (121) and (021) lattice fringes of α - Mo_2C and the (101) and (006) fringes of



Fig. 1 (a) Schematic illustration for the fabrication of MoC_x HNWs from MoO_x -amine NWs with tunable composition. (b) XRD patterns and (c) Mo 3d XPS profiles of the as-obtained MoC_x NWs.



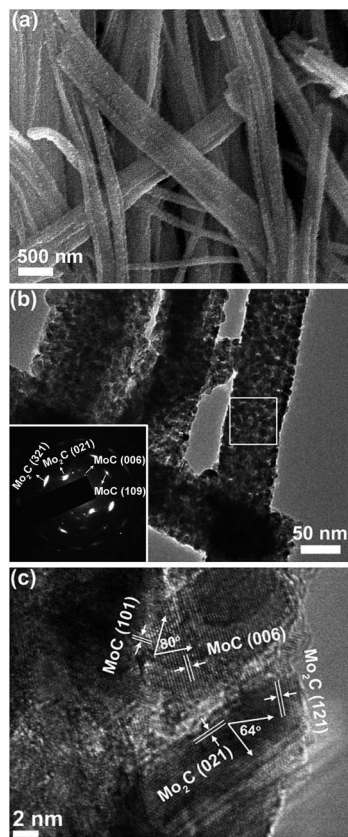


Fig. 2 (a) SEM, (b) TEM and (c) HR-TEM images of MoC–Mo₂C-31.4 HNWs. Inset of (b) is the SAED pattern obtained on the marked area.

η -MoC are identified in the high resolution TEM (HR-TEM, Fig. 2c). Noticeably, the interfaces between close-stacking MoC and Mo₂C NPs are visible, which would benefit synergy of the surface activity. Analogously, the Mo₂C and MoC NWs composed of the corresponding NPs are also verified through the TEM investigation, and in the MoC–Mo₂C-68.1 HNWs, both the MoC and Mo₂C NPs are identified (Fig. S6[†]). With nanosized crystallites, enriched nanoporosity, large surface areas, a conducting carbon matrix, and more importantly tunable Mo³⁺/Mo²⁺ centres, MoC–Mo₂C HNWs are expected to efficiently catalyse the HER.

To investigate the HER performance in an acidic electrolyte, the as-prepared MoC_x NWs were loaded onto glassy carbon electrodes (GCEs) with a mass loading of 0.14 mg cm⁻². Fig. 3a displays their polarization curves with iR -drop corrections in 0.5 M H₂SO₄, along with that of the benchmark Pt/C catalyst (40 wt% Pt on carbon black from Johnson Matthey) for reference. Among the MoC_x catalysts, MoC–Mo₂C-31.4 exhibits the highest activity. To achieve a current density (j) of -10 mA cm⁻², MoC–Mo₂C-31.4 requires a η_{10} of 126 mV, which is obviously lower than those of α -Mo₂C (182 mV) and η -MoC (232 mV). This suggests a synergic enhancement between Mo₂C and MoC in the HNWs. Meanwhile, the mechanically-mixed MoC–Mo₂C NWs with a similar MoC content of 30 wt% (denoted as MoC–Mo₂C-30 (mixed)) displayed a lower activity ($\eta_{10} = 222$ mV), indicating that the MoC–Mo₂C interfaces on the nanoscale in MoC–Mo₂C-31.4



Fig. 3 (a) Polarization curves and (b) Tafel plots for the HER on modified GCEs comprising (I) MoC–Mo₂C-31.4, (II) Mo₂C, (III) MoC–Mo₂C-68.1, (IV) MoC–Mo₂C-30 (mixed), (V) MoC, and (VI) commercial Pt/C in 0.5 M H₂SO₄. (c) Estimation of C_{dl} through plotting the current density variation ($\Delta j = (j_a - j_c)/2$, at 150 mV vs. RHE; data obtained from the CV in Fig. S7[†]) against scan rate to fit a linear regression, and (d) Nyquist plots (at $\eta = 200$ mV) of the above MoC_x electrocatalysts.

contribute to the efficient HER. Such a synergic effect is prohibited by the high percentage of MoC in the HNWs, and as this was increased to 68.1%, the activity obviously reduced. A summary of the HER activity of the above MoC_x is listed in Table 1.

Accordingly, the Tafel plots of the above carbides present the same order in HER kinetics (Fig. 3b and Table 1). Among them, MoC–Mo₂C-31.4 shows a η_{onset} of 38 mV and a Tafel slope of 43 mV dec⁻¹, which are obviously lower than those of Mo₂C, MoC, MoC–Mo₂C-68.1 and MoC–Mo₂C-30.0 (mixed). The small Tafel slope of MoC–Mo₂C-31.4 indicates a fast increase of the hydrogen generation rate with the applied overpotential, corresponding to the high activity presented in the polarization curves. According to the classic theory, the HER in acidic aqueous media proceeds in two steps (eqn (1)–(3)),^{40,41} where the * indicates the active site, and H* is a hydrogen atom bound to an active site. The first one is an electrochemical reduction step (H⁺ reduction, Volmer-reaction) with a Tafel slope of 118 mV dec⁻¹ (eqn (1)), and the second one (H_{ads} desorption) is either the ion and atom reaction (Heyrovsky-reaction) with a slope of 40 mV dec⁻¹ (eqn (2)) or the atom combination reaction (Tafel-reaction) with a slope of 30 mV dec⁻¹ (eqn (3)).^{8,40,41} Although the Tafel slope alone is insufficient to determine the specific mechanism, the evidently reduced slope for MoC–Mo₂C-31.4, compared with MoC and MoC–Mo₂C-68.1, still confirms the promoted Volmer-step in the HER kinetics.^{42,43} In addition, the exchange current density (j_0) of the above electrocatalysts was further calculated by extrapolating the Tafel plots, which is the most inherent measure of HER activity. As expected, the j_0 of 1.1×10^{-2} mA cm⁻² for MoC–Mo₂C-31.4 is higher than that of the other MoC_x (Table 1).



Table 1 Summary of the HER activity of MoC–Mo₂C–31.4, Mo₂C, MoC–Mo₂C–68.1, MoC–Mo₂C–30 (mixed), and MoC in 0.5 M H₂SO₄

Cat.	η_{10} (mV)	η_{onset} (mV)	Tafel slope (mV dec ⁻¹)	R_{ct}^a (Ω)	C_{dl}^b (mF cm ⁻²)	j_0^c (mA cm ⁻²)
MoC–Mo ₂ C–31.4	126	38	43	21.8	6.86	1.1×10^{-2}
Mo ₂ C	182	61	46	60.4	5.24	1.2×10^{-3}
MoC–Mo ₂ C–68.1	218	65	52	101.7	2.57	7.2×10^{-4}
MoC–Mo ₂ C–30 (mixed)	222	100	53	116	2.51	3.2×10^{-4}
MoC	232	105	62	145	2.06	5.0×10^{-4}

^a Data was measured at $\eta = 200$ mV. ^b Data was calculated according to the CV results (Fig. S7). ^c Exchange current densities (j_0) were obtained from Tafel curves by using extrapolation methods.



The electrochemical surface area (ECSA) and resistant charge-transfer (R_{ct}) were further evaluated to provide insight into the MoC_x electrocatalysts (Table 1, Fig. 3c and d). Although the accurate measurement of ECSA is difficult owing to the unclear capacitive behaviour, it can be visualized through calculating the double-layer capacitances (C_{dl}) which are proportional to the ECSA values.⁴⁴ An estimation of C_{dl} using the cyclic voltammograms (CV, Fig. S7†) in 0.5 M H₂SO₄ were alternatively utilized to provide a relative comparison.^{25,45} As shown in Fig. 3c, the C_{dl} of 6.86 mF cm⁻² presented by MoC–Mo₂C–31.4 is higher than those on α -Mo₂C (5.24 mF cm⁻²), η -MoC (2.06 mF cm⁻²), MoC–Mo₂C–68.1 (2.57 mF cm⁻²), and MoC–Mo₂C–30 (mixed) (2.51 mF cm⁻²). Regarding the C_{dl} associated with the active surface area, the current density divided by C_{dl} can further reflect the intrinsic activity,^{46,47} from which the remarkably high one for MoC–Mo₂C–31.4 indicates intrinsic optimization of the active-sites (Fig. S8†). Meanwhile, their electrochemical impedance spectroscopy (EIS) measurements show the consistent order in R_{ct} , and a R_{ct} as low as 21.8 Ω delivered by MoC–Mo₂C–31.4 confirms the rapid electron transport for hydrogen evolution (Fig. 3d).²⁸

It has been reported that the HER activity of MoC_x depends on the active Mo²⁺ and Mo³⁺ centres exposed on the catalyst surface,^{17,38} which present various Mo–H resulting from the different electron densities of Mo.¹⁶ As displayed in Fig. 4a, the HER activities of Mo₂C, MoC–Mo₂C–31.4, MoC–Mo₂C–68.1 and MoC are dependent on the variation of the ratio of active Mo³⁺/Mo²⁺ ($n_{3+/2+}$) on the surface, featured by the both of the current densities at $\eta = 0$ (j_0) and 150 mV (j_{150}). With a higher $n_{3+/2+}$ of 3.0 in comparison with Mo₂C ($n_{3+/2+} = 0.4$), MoC–Mo₂C–31.4 shows an obviously improved activity, which suggests that the enriched Mo³⁺ species with fewer electrons benefits HER. Furthermore, the narrowed valance-band (VB) distribution of MoC–Mo₂C–31.4 (Fig. S9†) indicates the lower electron density around the Fermi level (E_{F}) than that of Mo₂C. Regarding the strong hydrogen binding on Mo₂C and the consequently restricted H_{ads} desorption, the decreased electron density in the MoC–Mo₂C–31.4 HNWs would reduce the strength of Mo–H towards the promoted H_{ads} desorption and thus remarkably

improved the HER activity (Fig. 4b). Moreover, with $n_{3+/2+}$ increased to 7.2 and 10.9, respectively, MoC–Mo₂C–68.1 and MoC display further reduced electron density around E_{F} (Fig. S9†) and decreased HER activity in comparison with MoC–Mo₂C–31.4 (Fig. 4a). Their higher Tafel slopes (53 mV dec⁻¹ for MoC–Mo₂C–68.1, and 62 mV dec⁻¹ for MoC) suggest that the limitation of the Volmer step becomes more obvious, because of weak hydrogen-binding involving less electron donated by Mo (Fig. 4b). It's reasonable that the high activity of the MoC–Mo₂C–31.4 HNWs is ascribed to the optimized electronic properties of the MoC–Mo₂C interfaces with a well-defined composition.

The HER activity of MoC–Mo₂C–31.4 is superior to most of the carbide-based HER electrocatalysts that have ever been reported in acidic electrolytes (Table S4†). The η_{10} of 126 mV delivered by MoC–Mo₂C–31.4 is obviously lower than that of the reported nanoporous Mo₂C NWs (130 mV),²¹ MoCN NPs (140 mV),¹⁷ MoC_x nano-octahedrons (142 mV),⁴⁸ Mo₂C



Fig. 4 (a) j_0 (obtained by extrapolating the Tafel curves to $\eta = 0$ mV) and j_{150} (current density at $\eta = 150$ mV) of the above MoC_x, which are associated with the ratio of surface Mo³⁺/Mo²⁺ determined through XPS analysis. (b) Schematic illustration of the HER activity relying on the electron density of Mo in a series of MoC_x electrocatalysts.



nanotubes (172 mV),²⁶ and even that of supported MoC_x (Mo₂C/CNT-GR: 130 mV;²⁷ Mo₂C/N-doped CNT: 147 mV;⁴⁹ Mo₂C/RGO: 150 mV;²⁹ Mo₂C/CNT: 152 mV²⁸). To the best of our knowledge, the lower η_{10} than our MoC–Mo₂C-31.4 has been only achieved on GR or N-doped carbon encapsulated Mo₂C NPs, which require precise control over the N-doping and thickness of the carbon shells.^{38,45} In regard of the high mass loading of the previously reported electrocatalysts (0.21–2.0 mg cm⁻²), the remarkably low one in this work (0.14 mg cm⁻²) strongly supports the superior activity of the MoC–Mo₂C-31.4 HNWs. Meanwhile, the fast HER kinetics of MoC–Mo₂C-31.4 are also confirmed by its low η_{onset} (38 mV) and Tafel slope (43 mV dec⁻¹), which outperform most of the reported MoC_x (Table S4†). Furthermore, the HER performance of the MoC–Mo₂C-31.4 HNWs is among the best reported when compared with many representative noble-metal free electrocatalysts, *e.g.*, transition-metals and their carbides, nitrides, chalcogenides and phosphides (Table S4†).

Our MoC–Mo₂C-31.4 HNWs are also active for the HER in basic solution (1.0 M KOH), showing the best activity and kinetics in comparison with Mo₂C, MoC, MoC–Mo₂C-68.1 and MoC–Mo₂C-30 (mixed) (Fig. 5a and b). This shows good consistency with its high j_0 , high C_{dl} and low R_{ct} (Table S5, Fig. S10 and S11†). Obviously, the synergy between MoC and Mo₂C also promotes the HER performance in a basic electrolyte due to the optimized electronic properties of the Mo species. The η_{10} of 120 mV, η_{onset} of 33 mV and Tafel slope of 42 mV dec⁻¹, observed for MoC–Mo₂C-31.4, verify the outstanding activity performing among the best of the current MoC_x materials,^{18,20,23,25,26,34,45,49} and other noble-metal free electrocatalysts (Table S6†).

Interestingly, the activity of our MoC_x NWs in basic electrolyte is slightly higher than that in acidic solution. Similar situations have been observed with Mo₂C@N-doped carbon,³⁰ MoP,⁵⁰ Mo₂C NPs.¹⁸ This can be explained by the fact that the surface oxidized species on MoC–Mo₂C can be dissolved by KOH, exposing rich active-sites for the HER (Fig. S12†).

Another important criterion for a good electrocatalyst is its high durability. Herein, the long-term stability of MoC–Mo₂C-31.4 HNWs and the ability to continuously catalyse the generation of H₂ were examined through continuous cycling for 3000 cycles and chronoamperometry in both 0.5 M H₂SO₄ and 1.0 M KOH. At the end of the cycling procedure, the catalyst affords similar j - V curves to the initial cycle with negligible loss of the cathodic current (Fig. 5c), confirming the satisfactory durability in both acidic and basic electrolytes. When further evaluated through prolonged electrolysis at a fixed potential (Fig. 5d), MoC–Mo₂C-31.4 exhibited a catalytic current which remained at around 20 mA cm⁻² for over 20 hours in 0.5 M H₂SO₄. However, the current in 1.0 M KOH slightly decreased.

Conclusions

In summary, we have reported the facile fabrication of MoC–Mo₂C HNWs *via* the controlled carbonization of MoO_x-amine. This strategy presents significance in regulating the crystalline structure, composition and electronic properties toward efficient HER. Showing an optimized electron density on the carbide surface, the MoC–Mo₂C-31.4 HNWs exhibit high activity and good stability in both acidic and basic solutions. This work will open up new opportunities to develop high-performance electrocatalysts *via* rational engineering of nanostructures and interfaces.

Experimental section

Catalyst preparation

Improved from our previous reports,^{51,52} MoAn-4.0 and MoAn-3.5 NWs were typically synthesized as follows: 2.48 g of ammonium heptamolybdate tetrahydrate ((NH₄)₆Mo₇O₂₄·4H₂O) was dissolved in 40 mL of water consisting of 3.28 mL of Aniline. Then, 1 M HCl aqueous solution was added to adjust the pH level to 4.0 for generating MoAn-4.0, and 3.5 for achieving MoAn-3.5, respectively. After reaction at 50 °C for 4 hour in an oil bath, the products were filtered and thoroughly washed with ethanol, and then dried at 50 °C overnight. MoMeAn-4.0 NWs were prepared through a similar process to that of MoAn, replacing the aniline with 3.83 g of *p*-methylaniline.

The as-obtained MoO_x-based hybrids (MoAn-4.0, MoAn-3.5 and MoMeAn-4.0) were transferred into a tube furnace and kept under an Ar flow for 4.0 h in order to remove air before heating. Then, the sample was heated to a target temperature and held for 5 h. The details for carbonization are listed in Table S1.†

Physical measurements

SEM and TEM investigations were undertaken on a ZEISS ULTRA55 and a JEOL JEM 2100F, respectively. XRD analysis was

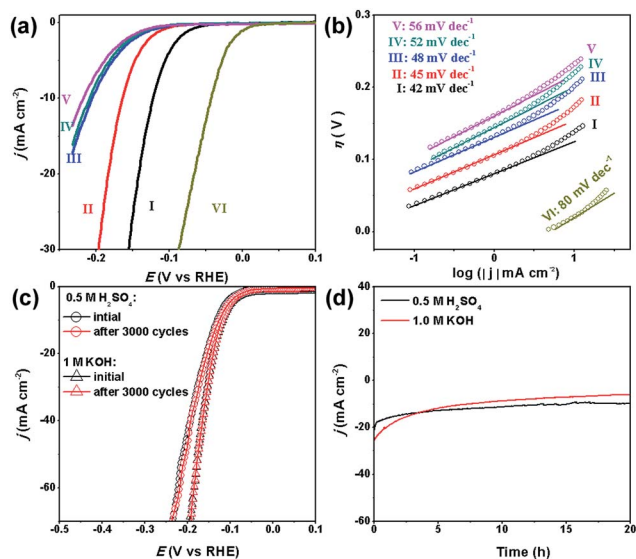


Fig. 5 (a) Polarization curves and (b) Tafel plots for the HER on modified GCEs comprising (I) MoC–Mo₂C-31.4, (II) Mo₂C, (III) MoC–Mo₂C-68.1, (IV) MoC–Mo₂C-30 (mixed), (V) MoC, and (VI) commercial Pt/C in 1.0 M KOH. (c) Stability of the MoC/Mo₂C-31.4 modified electrodes with an initial polarization curve and after 3000 cycles in 0.5 M H₂SO₄ and 1.0 M KOH, and (d) the long-term durability tests at $\eta = 190$ mV.



performed on a Bruker D8 diffractometer using Cu K α radiation ($\lambda = 1.54056 \text{ \AA}$). XPS was processed on a Perkin-Elmer PHI X-tool, using C 1s (B. E. = 284.6 eV) as a reference. TGA/DSC was tested on a NETZSCH STA449F3 under an air flow. FT-IR spectra were collected with a Nicolet 6700 FTIR spectrometer. The composition of the NWs was determined using ICP (for Mo), CHN elemental analysis using a Vario EL Elementar (for C, H and N) and an internal standard quantification in XRD (for the ratio of MoC/Mo₂C). N₂ adsorption-desorption isotherms were recorded on an automatic gas adsorption analyzer (Quantachrome Autosorb-iQ-MP). Raman spectra were recorded on a Raman spectrometer (Horiba), with an excitation laser wavelength of 632.81 nm.

Electrochemical measurements

The MoC_x electrocatalysts were loaded onto GCEs for testing in 0.5 M H₂SO₄ and 1.0 M KOH solutions using a typical three-electrode setup. Typically, 4 mg of catalyst and 40.0 μL of 5 wt% Nafion solution were dispersed in 1 mL of 4 : 1 v/v water/ethanol through at least 30 min of sonication to form a homogeneous ink. For the test in 1.0 M KOH, 10 μL of polyvinylidene fluoride (5 wt%) was further added into the above ink. Then 2.5 μL of catalyst ink was loaded onto a GCE of 3 mm in diameter. Linear sweep voltammetry (LSV) was conducted with the scan rate of 2 mV s⁻¹ in 0.5 mol L⁻¹ H₂SO₄ or 1.0 M KOH on a potentiostat of CHI760 (CH Instruments), using a saturated calomel electrode as the reference electrode, and a graphite electrode as the counter electrode. All of the potentials reported in our manuscript were referenced to a reversible hydrogen electrode (RHE) by adding a value of (0.241 + 0.059 pH) V. AC impedance measurements were carried out in the same configuration at $\eta = 200 \text{ mV}$ from 0.01 to 1 000 000 Hz and an amplitude of 5 mV.

Acknowledgements

This work is financially supported by the National Basic Research Program of China (2013CB934101), the National Natural Science Foundation of China (21373102 and 21433002) and the Fundamental Research Funds for the Central Universities (21615402). Q. S. Gao also thanks the support from the Natural Science Foundation of Guangdong Province (2015A030306014 and 2014TQ01N036) and the Guangdong Higher Education Institute (YQ2013022).

Notes and references

- H. B. Gray, *Nat. Chem.*, 2009, **1**, 7–8.
- M. S. Dresselhaus and I. L. Thomas, *Nature*, 2001, **414**, 332–337.
- G. W. Crabtree, M. S. Dresselhaus and M. V. Buchanan, *Phys. Today*, 2004, **57**, 39–44.
- T. R. Cook, D. K. Dogutan, S. Y. Reece, Y. Surendranath, T. S. Teets and D. G. Nocera, *Chem. Rev.*, 2010, **110**, 6474–6502.
- C. G. Morales-Guio, L. A. Stern and X. Hu, *Chem. Soc. Rev.*, 2014, **43**, 6555–6569.
- X. X. Zou and Y. Zhang, *Chem. Soc. Rev.*, 2015, **44**, 5148–5180.
- M. S. Faber and S. Jin, *Energy Environ. Sci.*, 2014, **7**, 3519–3542.
- M. Zeng and Y. G. Li, *J. Mater. Chem. A*, 2015, **3**, 14942–14962.
- J. R. McKone, S. C. Marinescu, B. S. Brunschwig, J. R. Winkler and H. B. Gray, *Chem. Sci.*, 2014, **5**, 865–878.
- P. C. K. Vesborg, B. Seger and I. Chorkendorff, *J. Phys. Chem. Lett.*, 2015, **6**, 951–957.
- J. Xie, S. Li, X. Zhang, J. Zhang, R. Wang, H. Zhang, B. Pan and Y. Xie, *Chem. Sci.*, 2014, **5**, 4615–4620.
- Y. N. Regmi, G. R. Waetzig, K. D. Duffee, S. M. Schmuecker, J. M. Thode and B. M. Leonard, *J. Mater. Chem. A*, 2015, **3**, 10085–10091.
- C. Wan, Y. N. Regmi and B. M. Leonard, *Angew. Chem., Int. Ed.*, 2014, **53**, 6407–6410.
- Q. S. Gao, N. Liu, S. N. Wang and Y. Tang, *Nanoscale*, 2014, **6**, 14106–14120.
- H. H. Hwu and J. G. Chen, *Chem. Rev.*, 2005, **105**, 185.
- R. Michalsky, Y. J. Zhang and A. A. Peterson, *ACS Catal.*, 2014, **4**, 1274–1278.
- Y. Zhao, K. Kamiya, K. Hashimoto and S. Nakanishi, *J. Am. Chem. Soc.*, 2015, **137**, 110–113.
- L. Ma, L. R. L. Ting, V. Molinari, C. Giordano and B. S. Yeo, *J. Mater. Chem. A*, 2015, **3**, 8361–8368.
- C. Tang, A. Sun, Y. Xu, Z. Wu and D. Wang, *J. Power Sources*, 2015, **296**, 18–22.
- H. Vrubel and X. Hu, *Angew. Chem., Int. Ed.*, 2012, **51**, 12703–12706.
- L. Liao, S. Wang, J. Xiao, X. Bian, Y. Zhang, M. D. Scanlon, X. Hu, Y. Tang, B. Liu and H. H. Girault, *Energy Environ. Sci.*, 2014, **7**, 387–392.
- C. Ge, P. Jiang, W. Cui, Z. Pu, Z. Xing, A. M. Asiri, A. Y. Obaid, X. Sun and J. Tian, *Electrochim. Acta*, 2014, **134**, 182–186.
- P. Xiao, Y. Yan, X. Ge, Z. Liu, J.-Y. Wang and X. Wang, *Appl. Catal., B*, 2014, **154**, 232–237.
- K. Zhang, C. Li, Y. Zhao, X. Yu and Y. Chen, *Phys. Chem. Chem. Phys.*, 2015, **17**, 16609–16614.
- H. B. Wu, B. Y. Xia, L. Yu, X.-Y. Yu and X. W. Lou, *Nat. Commun.*, 2015, **6**, 6512.
- F. X. Ma, H. B. Wu, C. Y. Xu and X. W. Lou, *Angew. Chem., Int. Ed.*, 2015, 15395–15399.
- D. H. Youn, S. Han, J. Y. Kim, J. Y. Kim, H. Park, S. H. Choi and J. S. Lee, *ACS Nano*, 2014, **8**, 5164–5173.
- W. F. Chen, C. H. Wang, K. Sasaki, N. Marinkovic, W. Xu, J. T. Muckerman, Y. Zhu and R. R. Adzic, *Energy Environ. Sci.*, 2013, **6**, 943.
- C. He and J. Tao, *Chem. Commun.*, 2015, **51**, 8323–8325.
- Y. Liu, G. Yu, G. D. Li, Y. Sun, T. Asefa, W. Chen and X. Zou, *Angew. Chem., Int. Ed.*, 2015, **54**, 10752–10757.
- J. Zhu, K. Sakaushi, G. Clavel, M. Shalom, M. Antonietti and T.-P. Fellingner, *J. Am. Chem. Soc.*, 2015, **137**, 5480–5485.
- J. Greeley, T. F. Jaramillo, J. Bonde, I. B. Chorkendorff and J. K. Norskov, *Nat. Mater.*, 2006, **5**, 909–913.
- C. Wan and B. M. Leonard, *Chem. Mater.*, 2015, **27**, 4281–4288.
- K. Xiong, L. Li, L. Zhang, W. Ding, L. S. Peng, Y. Wang, S. G. Chen, S. Y. Tan and Z. D. Wei, *J. Mater. Chem. A*, 2015, **3**, 1863–1867.



- 35 V. Heine, *Phys. Rev. A*, 1967, **153**, 673.
- 36 L. Ramqvist, *Appl. Phys.*, 1971, **42**, 2113–2127.
- 37 C. Wan, N. A. Knight and B. M. Leonard, *Chem. Commun.*, 2013, **49**, 10409–10411.
- 38 R. G. Ma, Y. Zhou, Y. F. Chen, P. X. Li, Q. Liu and J. C. Wang, *Angew. Chem., Int. Ed.*, 2015, **54**, 14723–14727.
- 39 M. Xiang, D. Li, W. Li, B. Zhong and Y. Sun, *Catal. Commun.*, 2007, **8**, 513–518.
- 40 S. A. Vilekar, I. Fishtik and R. Datta, *J. Electrochem. Soc.*, 2010, **157**, B1040–B1050.
- 41 C. G. Morales-Guio, L. A. Stern and X. L. Hu, *Chem. Soc. Rev.*, 2014, **43**, 6555–6569.
- 42 N. Liu, Y. L. Guo, X. Y. Yang, H. L. Lin, L. C. Yang, Z. P. Shi, Z. W. Zhong, S. N. Wang, Y. Tang and Q. S. Gao, *ACS Appl. Mater. Interfaces*, 2015, **7**, 23741–23749.
- 43 N. Liu, L. C. Yang, S. N. Wang, Z. W. Zhong, S. N. He, X. Y. Yang, Q. S. Gao and Y. Tang, *J. Power Sources*, 2015, **275**, 588–594.
- 44 M. R. Gao, M. K. Y. Chan and Y. G. Sun, *Nat. Commun.*, 2015, **6**, 7493.
- 45 Y. Liu, G. Yu, G.-D. Li, Y. Sun, T. Asefa, W. Chen and X. Zou, *Angew. Chem., Int. Ed.*, 2015, **54**, 10752–10757.
- 46 D. Merki, S. Fierro, H. Vrubel and X. L. Hu, *Chem. Sci.*, 2011, **2**, 1262–1267.
- 47 N. Liu, L. Yang, S. Wang, Z. Zhong, S. He, X. Yang, Q. Gao and Y. Tang, *J. Power Sources*, 2015, **275**, 588–594.
- 48 H. B. Wu, B. Y. Xia, L. Yu, X. Y. Yu and X. W. Lou, *Nat. Commun.*, 2015, **6**, 6512.
- 49 K. Zhang, Y. Zhao, D. Fu and Y. Chen, *J. Mater. Chem. A*, 2015, **3**, 5783–5788.
- 50 P. Xiao, M. A. Sk, L. Thia, X. Ge, R. J. Lim, J.-Y. Wang, K. H. Lim and X. Wang, *Energy Environ. Sci.*, 2014, **7**, 2624–2629.
- 51 Q. S. Gao, C. X. Zhang, S. H. Xie, W. M. Hua, Y. H. Zhang, N. Ren, H. L. Xu and Y. Tang, *Chem. Mater.*, 2009, **21**, 5560–5562.
- 52 Q. Gao, S. Wang, H. Fang, J. Weng, Y. Zhang, J. Mao and Y. Tang, *J. Mater. Chem.*, 2012, **22**, 4709–4715.

