



**Bismuth Phosphate Nanoparticle Catalyst for Direct
Oxidation of Methane into Formaldehyde
Invitation to contribute to the Catalysis Science &
Technology special collection "Integrated Approaches for
Methane Activation"**

Journal:	<i>Catalysis Science & Technology</i>
Manuscript ID	CY-ART-04-2023-000590.R1
Article Type:	Paper
Date Submitted by the Author:	07-Jul-2023
Complete List of Authors:	<p>Matsuda, Aoi; Tokyo Institute of Technology Institute of Innovative Research, Laboratory for Materials and Structures Laboratory, Institute of Innovative Research</p> <p>Obara, Kazuhiko; Tokyo Institute of Technology Institute of Innovative Research, Laboratory for Materials and Structures Laboratory, Institute of Innovative Research</p> <p>Ishikawa, Atsushi; Tokyo Institute of Technology, Department of Transdisciplinary Science and Engineering, School of Environment and Society</p> <p>Tsai, Meng-Hsuan; National Synchrotron Radiation Research Center</p> <p>Wang, Chia-Hsin; National Synchrotron Radiation Research Center,</p> <p>Lin, Yu-Chuan; National Cheng Kung University, Chemical Engineering;</p> <p>Hara, Michikazu; Tokyo Institute of Technology Institute of Innovative Research, Laboratory for Materials and Structures Laboratory, Institute of Innovative Research</p> <p>Kamata, Keigo; Tokyo Institute of Technology, Laboratory for Materials and Structures Laboratory, Institute of Innovative Research</p>

ARTICLE

Bismuth Phosphate Nanoparticle Catalyst for Direct Oxidation of Methane into Formaldehyde

Received 00th January 20xx,
Accepted 00th January 20xx

Aoi Matsuda,^a Kazuhiko Obara,^a Atsushi Ishikawa,^b Meng-Hsuan Tsai,^c Chia-Hsin Wang,^c Yu-Chuan Lin,^d Michikazu Hara,^a Keigo Kamata^{*a}

DOI: 10.1039/x0xx00000x

The direct oxidation of methane (CH₄) to formaldehyde (HCHO) with molecular oxygen (O₂) as the sole oxidant was studied over various bismuth-based catalysts (BiPO₄, α-Bi₂O₃, β-Bi₂O₃) using a fixed-bed flow reactor. The catalytic activity of monoclinic BiPO₄ nanoparticles (BiPO₄-DEG) synthesized in a mixed solvent of diethylene glycol (DEG) and water for the direct oxidation of CH₄ was the highest among the catalysts tested. In high temperature region, BiPO₄-DEG was more selective for HCHO formation than FePO₄ nanoparticles. Based on mechanistic studies including the catalyst effect, kinetics, pulse-reaction experiments, infrared (IR) spectroscopy, *operando* near ambient pressure X-ray photoelectron spectroscopy (NAP-XPS), and density functional theory (DFT) calculations, surface active oxygen species generated on BiPO₄ possibly react with CH₄ to give HCHO as the primary product. In contrast, the phosphate units of FePO₄ nanoparticles react with CH₄ followed by rapid reoxidation to FePO₄.

1. Introduction

Methane (CH₄) has attracted attention as an important raw material due to its abundance around the world as a main component of natural gas and a low emitter of greenhouse gases such as carbon dioxide (CO₂) compared to coal and oil.¹ However, CH₄ is mainly used as an energy source for heating, cooking, and power generation. The use of CH₄ as a chemical feedstock is very small due to the difficulty in activating the strong C–H bond (440 kJ mol⁻¹).² Current CH₄ conversion into commodity chemicals and fuels is limited to indirect pathways via synthesis gas (CO + H₂) produced by energy- and capital-intensive reforming processes.³ Therefore, the development of catalytic processes that can directly convert CH₄ into useful chemicals and fuels is an important and challenging subjects, and various effective thermocatalytic,^{2,4–8} electrocatalytic,⁹ and plasma- or electric-field assisted systems¹⁰ have been reported for oxidative CH₄ upgrading and non-oxidative dehydrogenative aromatization.^{11,12}

Various effective solid materials based on metal-exchanged zeolites,^{14–18} metal oxides,^{19–22} supported catalysts,^{23–25} metal phosphates,^{26–36} and metal organic frameworks^{37,38} can

function as efficient catalysts for oxidative upgrading of CH₄ such as oxidative coupling to ethylene (C₂H₄), oxygenation to methanol (CH₃OH) and/or formaldehyde (HCHO), and oxidative halogenation using O₂, H₂O₂, and N₂O as oxidants. In particular, V- and Mo-based catalysts and B₂O₃/Al₂O₃ are efficient catalysts for the oxidation of CH₄ into HCHO which is an important raw material as resins and polyfunctional alcohols.^{39–42} The performance of V- and Mo-based catalysts is improved by the metal loading amounts and space velocity, and Cu-MoO_x catalysts selectively give HCHO in 1.0% yield (62% select.) for the CH₄ oxidation at 700 °C in the presence of water vapor.⁴¹ Non-metallic B₂O₃-based catalysts exhibit high HCHO yield and selectivity, and molecular O₂ bonded to tri-coordinated BO₃ centers on B₂O₃ surfaces has been proposed as an active oxidant for CH₄ activation.⁴²

Among the solid catalyst materials, we have also focused on metal phosphates with unique surface redox and acid-base properties for the direct oxidation of CH₄ with O₂ as the sole oxidant.^{28,43,44} Monoclinic cerium orthophosphate (CePO₄) nanorods efficiently catalyze the oxidative coupling of CH₄ in an electric field without the need for external heating.^{28,43} Trigonal iron phosphate (FePO₄) nanoparticles exhibits high activity for the selective oxidation of CH₄ into HCHO. The weakly-basic phosphate units likely contribute to the suppression of complete oxidation to CO₂.⁴⁴ While the redox-active Lewis acidic metal sites of metal phosphates play an important role in the activation of CH₄ and O₂, the effect of metals and the reaction mechanism on the direct oxidation of CH₄ is still unclear. Herein, we focus on bismuth, which is used as the main catalyst component in industrial propylene oxidation processes.⁴⁵ Although bismuth phosphates (Fig. 1) have been mostly investigated for photocatalytic reactions,^{46–51} their application to other reactions (e.g., oxidative

^a Laboratory for Materials and Structures, Institute of Innovative Research, Tokyo Institute of Technology, 4259 Nagatsuta-cho, Midori-ku, Yokohama, Kanagawa 226-8503, Japan. E-mail: kamata.k.ac@m.titech.ac.jp

^b Department of Transdisciplinary Science and Engineering, School of Environment and Society, Tokyo Institute of Technology, 2-12-1 Ookayama, Meguro-ku, Tokyo 152-8550, Japan

^c National Synchrotron Radiation Research Center, 101 Hsin-Ann Rd, 30076, Hsinchu, Taiwan.

^d Department of Chemical Engineering, National Cheng Kung University, 1 University Rd., Tainan, 70101, Taiwan.

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x

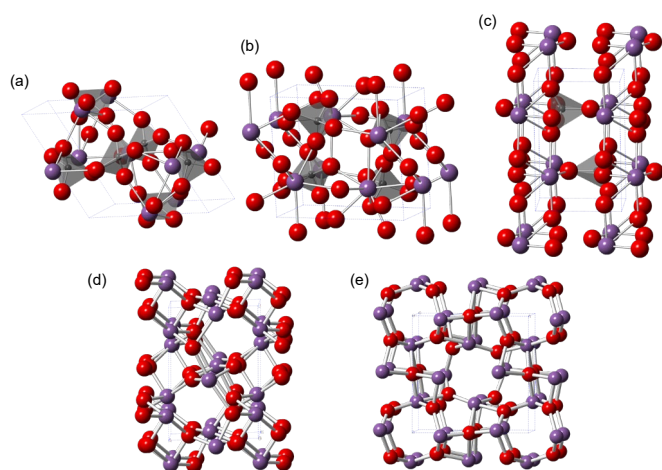


Fig. 1 Structures of (a) trigonal $\text{BiPO}_4 \cdot (\text{H}_2\text{O})_{0.67}$, (b) monoclinic BiPO_4 ($P2_1/n$), and (c) monoclinic BiPO_4 ($P2_1/m$), (d) monoclinic $\alpha\text{-Bi}_2\text{O}_3$, and (e) tetragonal $\beta\text{-Bi}_2\text{O}_3$. Purple, gray, and red spheres represent Bi, P, and O atoms, respectively.

dehydrogenation,^{52–54} ammoxidation,⁵⁵ decomposition,⁵⁶ isomerization,⁵⁷ aldol condensation⁵⁸) including the direct oxidation of CH_4 has not been sufficiently explored.^{23,26}

In this paper, we report the selective oxidation of CH_4 to HCHO with molecular oxygen (O_2) as the sole oxidant over a BiPO_4 catalyst using a fixed-bed flow reactor. BiPO_4 nanoparticles ($\text{BiPO}_4\text{-DEG}$) synthesized in a mixed solvent in DEG/water exhibit higher catalytic activity and selectivity for HCHO than other bismuth-containing catalysts (Fig. 1) and FePO_4 nanoparticles.⁴⁴ The mechanistic studies including the catalyst effect, pulse experiments, kinetics, operando analysis and density functional theory (DFT) calculations indicate that surface oxygen species generated on BiPO_4 possibly react with CH_4 to give HCHO as a primary product.

2. Experimental Section

2.1. Instruments

X-ray diffraction (XRD), energy dispersive X-ray fluorescence spectroscopy (ED-XRF), infrared Fourier transform infrared spectroscopy (FT-IR), thermogravimetry-differential thermal analysis (TG-DTA), H_2 temperature-programmed reduction ($\text{H}_2\text{-TPR}$), nitrogen adsorption-desorption, scanning electron microscopy (SEM), transmission electron microscopy (TEM), and X-ray photoelectron spectroscopy (XPS) were performed using previously described instruments.^{44, 59–61} The details are described in the Electronic Supplementary Information (ESI).

2.2. Synthesis of $\text{BiPO}_4\text{-DEG}$

$\text{NH}_4\text{H}_2\text{PO}_4$ (1.035 g, 9 mmol) was dissolved in a mixed solution of diethylene glycol (DEG)/water (75 mL, 1/1 v/v). A DEG solution (30 mL) containing $\text{Bi}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ (4.37 g, 9 mmol) was added dropwise into this phosphate solution followed by stirring for 60 min at room temperature. The resulting precipitates were collected by centrifugation, washed with ethanol (40 mL \times 3), and dried at 110 °C

overnight to obtain $\text{BiPO}_4 \cdot (\text{H}_2\text{O})_{0.67}$ as a precursor. This precursor was calcined at 600 °C for 5 h to give $\text{BiPO}_4\text{-DEG}$ (2.54 g, 93% yield).

2.3. Synthesis of $\text{BiPO}_4\text{-HT}$

$\text{BiPO}_4\text{-HT}$ was synthesized by a hydrothermal (HT) reaction. $\text{Bi}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ (6.00 mmol, 2.91 g) and $(\text{NH}_4)_2\text{HPO}_4$ (6.00 mmol, 0.792 g) were added to water (70 mL) and stirred for 30 min at room temperature. The resulting solution was transferred into a stainless steel autoclave with a Teflon vessel liner (TAF-SR type, Taiatsu Techno Corporation). After the solution was heated at 180 °C for 18 h, the precipitates were collected by filtration and washed with water (200 mL). The resulting precipitates were calcined at 600 °C for 5 h and the $\text{BiPO}_4\text{-HT}$ catalyst was obtained (1.75 g, 96% yield).

2.4. Catalytic oxidation of CH_4 with O_2

The oxidation of CH_4 with O_2 over various bismuth-based catalysts was conducted in a fixed-bed continuous-flow reactor operated at atmospheric pressure. All of the catalysts were pressed into pellets, crushed, and sieved to 32–42 meshes before the reaction. The catalyst (100 mg) was loaded into a quartz reactor (2 mm inner diameter at the catalyst bed portion) over a plug of quartz wool. When using a quartz reactor with larger inner diameter (4 mm) under the conditions in Fig. 3(d), the HCHO yield was not changed but the CO yield increased, which likely indicates quenching effect. A reaction gas containing $\text{CH}_4/\text{O}_2/\text{N}_2$ in a molar ratio of 20/20/60 was used and the total gas flow rate was 10 sccm (i.e., $\text{CH}_4/\text{O}_2/\text{N}_2 = 2/2/6$ sccm). After introduction of the reaction gas flow to the reactor, the reaction temperature was increased from room temperature to 600 °C at a heating rate of ca. 40 °C min^{-1} and then held for 60 min. After the first sampling of the reaction gas, the temperature was decreased by 10 °C to 470 °C (420 °C in the case of FePO_4) every 60 min with periodic analysis of the reaction gas. The products (CO, CO_2 , CH_3OH , HCHO, CH_3OCH_3 , C_2H_6 , C_2H_4) were analyzed using on-line gas chromatography (Shimadzu GC-8A) with a thermal conductivity detector (TCD) and two packed columns (a mixed column of Porapak-QS/-N and molecular sieves 5A). All of the lines and valves between the reactor exit and the gas chromatograph were heated to 120–130 °C to prevent condensation of the products. Details of the calculations of CH_4 conversion, yield, and selectivity are as follows: CH_4 conversion (%) = carbon of (CO, CO_2 , HCHO)/carbon of input $\text{CH}_4 \times 100$. Yield (%) = carbon of product/carbon of input $\text{CH}_4 \times 100$. Selectivity (%) = yield/ CH_4 conversion $\times 100$. Carbon balance (%) = (carbon of (CO, CO_2 , HCHO) + carbon of output CH_4) / carbon of input $\text{CH}_4 \times 100$. In each case, the carbon balance was in the range of 98.7 \pm 1.4%.

2.5. Pulse-reaction experiments for CH_4 oxidation

The pulse-reaction experiments were performed using a quartz reactor (4 mm inner diameter at the catalyst bed portion) over a plug of quartz wool. The exit gas was directly connected to a gas chromatograph with a TCD (Shimadzu, GC-8A), and HCHO/ CO_2 and CO were analyzed using Porapak-N and molecular sieves 5A columns, respectively. The details of the pulse-reactions of He-treated $\text{BiPO}_4\text{-DEG}$ with (i) CH_4 or (ii) CH_4/O_2 pulse (1 mL, 1/1 v/v) are as follows. Prior to the pulse-reaction experiments, $\text{BiPO}_4\text{-DEG}$ (100 mg) was pretreated in a He flow (20 sccm) at 600 °C for 30 min followed by (i)

CH₄ pulse (1 mL) or (ii) CH₄/O₂ pulse (1 mL, 1/1 v/v) through the catalyst bed at 600 °C.

2.6. Computational details

The energy evaluation and geometry optimization of the atomic positions were carried out according to the following procedure. The initial atomic positions for the oxides were obtained from the experimental structure of monazite-type monoclinic BiPO₄ (*P*₂1/*n*) taken from the inorganic crystal structure database (ICSD) with ID = 426231. The unit cell consists of a 2×2×3 supercell, and the lower 2/3 of the unit cell was fixed during the geometry optimization. The core electrons were represented by the projector augmented-wave (PAW) method,⁶² and the valence electrons were expanded by the plane wave basis set up to a cutoff energy of 400 eV. The meta-GGA SCAN functional was used as the exchange-correlation functional in the DFT calculations.⁶³ The Gaussian smearing method with $\sigma = 0.1$ was used throughout for the smearing of the electron occupation near the Fermi level. The convergence thresholds for the electronic state calculation and geometry optimization were set to 1.0×10^{-5} eV and 0.03 eV/Å in energy and force, respectively. Integration in the reciprocal lattice space was performed by numerical integration using *k*-points, which were placed such that the spacing between them was 0.3 \AA^{-1} . The gamma point was always included. For isolated molecule calculations (H₂, O₂, CH₃, and CH₄), a single *k*-point was placed on the gamma point. A vacuum layer with a thickness of 12 Å was placed between the slabs, and a dipole correction in the *z*-direction was introduced to remove the artificial interaction between slabs. All the calculations were performed with the Vienna *ab initio* simulation package (VASP) version 5.4.^{64,65}

2.8. Operando near ambient pressure X-ray photoelectron spectroscopy (NAP-XPS) experiment

NAP-XPS analysis was performed at the Taiwan Light Source (TLS) beamline 24A of the National Synchrotron Radiation Research Center (NSRRC), Taiwan. The tested sample was pelleted and the spectra were recorded at 550 °C under evacuation and in O₂ atmosphere (0.1 mbar) in the NAP-XPS chamber. P 2p signal at 133.2 eV was used to correct the energy shift.

3. Results and Discussion

3.1. Synthesis and characterization of bismuth phosphate nanoparticles

The low solubility of Bi species (e.g., Bi(NO₃)₃) in aqueous media typically requires severe reaction conditions such as hydrothermal treatment to obtain bismuth phosphate (BiPO₄) catalyst materials, which results in low specific surface areas. Thus, solvothermal and related synthesis methods are more effective for the synthesis of BiPO₄ nanoparticles. We also synthesized BiPO₄ nanoparticles (BiPO₄-DEG) by the calcination of a precursor, which was prepared by the reaction of Bi(NO₃)₃·5H₂O and NH₄H₂PO₄ in a mixed solution of diethylene glycol (DEG)/water, in air at 600 °C.

The XRD patterns for the precursor and BiPO₄-DEG showed the formation of hydrated bismuth phosphate in the trigonal system (BiPO₄·(H₂O)_{0.67}) and a mixture of monoclinic BiPO₄

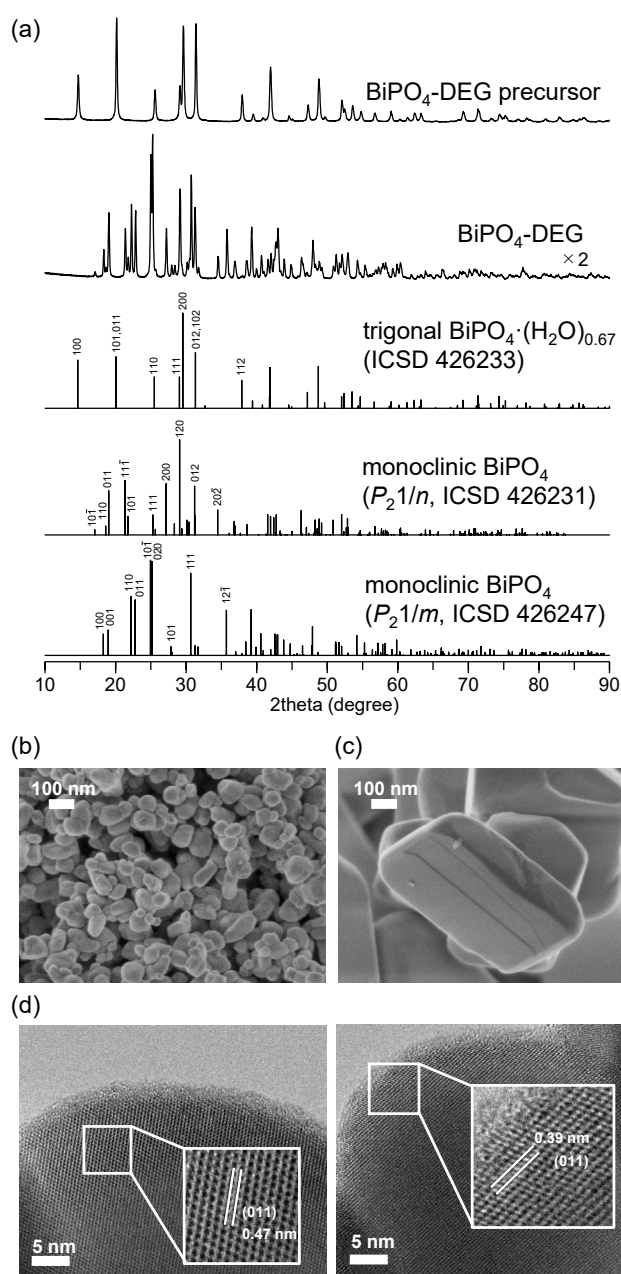


Fig. 2 (a) XRD patterns for BiPO₄-DEG precursor, BiPO₄-DEG, trigonal BiPO₄·(H₂O)_{0.67} (ICSD 426233), monoclinic BiPO₄ (*P*₂1/*n*, ICSD 426231), and monoclinic BiPO₄ (*P*₂1/*m*, ICSD 426247). SEM images for (b) BiPO₄-DEG and (c) BiPO₄-HT. (d) TEM images for BiPO₄-DEG.

(*P*₂1/*n* and *P*₂1/*m*), respectively (Fig. 2(a)). Braque and co-workers reported that the trigonal phase of BiPO₄·(H₂O)_{0.67} (Fig. 1(a)) is metastable and irreversibly transforms to the monazite-type structure (*P*₂1/*n*, Fig. 1(b)) and that this monazite-type BiPO₄ slowly transforms into the high-temperature monoclinic form (*P*₂1/*m*, Fig. 1(c)) when heated above 600 °C.⁶⁶ No impurity phases such as bismuth phosphates, bismuth oxides, or phosphorous oxides were observed. Elemental analysis of BiPO₄-DEG using energy dispersive X-ray fluorescence spectroscopy (ED-XRF) showed that the molar ratio of Bi/P was 1/1, which also supports the high purity. On the other hand,

Table 1 Specific surface area, bulk content, and particle and crystallite size of the bismuth-based catalysts

Entry	Catalyst	S_{BET} ($\text{m}^2 \text{g}^{-1}$)	Crystallite size ^a (nm)
1	BiPO ₄ -DEG precursor	14	38 (110)
2	BiPO ₄ -DEG	10	$P_{21/n}$: 46 (10-1) $P_{21/m}$: 51 (12-1)
3	BiPO ₄ -HT	<1	93 (10-1)
4	α -Bi ₂ O ₃	1	97 (002)
5	β -Bi ₂ O ₃	10	70 (201)
6 ^b	FePO ₄	22	33 (100) 22 (200)

^a Calculated by the XRD peaks using Rigaku PDXL2 software. ^b Data from ref. 44.

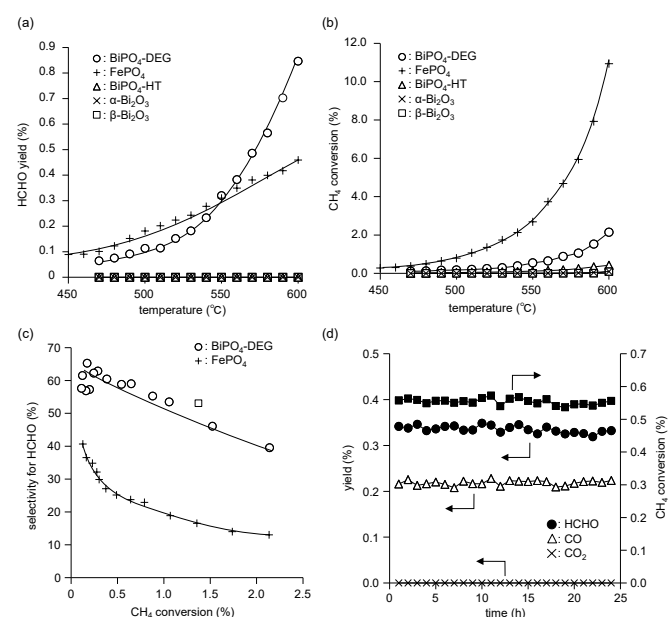


Fig. 3 (a) HCHO yield and (b) CH₄ conversion as a function of reaction temperature and (c) selectivity for HCHO as a function of CH₄ conversion over BiPO₄-DEG, FePO₄, BiPO₄-HT, α -Bi₂O₃, and β -Bi₂O₃ catalysts. Reaction conditions: catalyst (100 mg), CH₄/O₂/N₂ (2/2/6 sccm), 420–600 °C. (d) Time-on-stream performance of BiPO₄-DEG for oxidation of CH₄. Reaction conditions: BiPO₄-DEG (100 mg), CH₄/O₂/N₂ (2/2/6 sccm), 550 °C.

only the monazite-type structure was observed for BiPO₄-HT synthesized by the hydrothermal reaction of Bi(NO₃)₃ and (NH₄)₂HPO₄ at 180 °C followed by calcination at 600 °C in a similar manner to that of previous reports (Fig. S1).^{47,49}

The specific surface area of BiPO₄-DEG was 10 m² g⁻¹, which is much larger than that of BiPO₄-HT (<1 m² g⁻¹) (Table 1). SEM observations of BiPO₄-DEG showed the formation of spherical nanoparticles with estimated particle sizes of ca. 50–100 nm (Fig. 2(b)), while large particles with sizes of hundreds of nanometers were observed for BiPO₄-HT (Fig. 2(c)). These nanoparticle sizes were in reasonable agreement with the grain sizes ($d = 46$ and 51 nm for BiPO₄ ($P_{21/n}$ and $P_{21/m}$), respectively) calculated from the (10-1) and (12-1) diffraction lines, respectively, using Scherrer's equation. A similar

morphology and size distribution of the nanoparticles were observed by TEM, with clear lattice fringes throughout the particles indicating their crystallinity (Fig. 2(d)). The distances between fringes of different particles were 0.47 and 0.39 nm, assigned to the d -spacing for the (011) planes of monazite-type ($P_{21/n}$) and high-temperature monoclinic BiPO₄ ($P_{21/m}$), respectively.^{47,50}

3.2. Catalytic oxidation of CH₄ into HCHO with O₂

The catalyst effect of bismuth-based materials (BiPO₄-DEG, BiPO₄-HT, α -Bi₂O₃ (Fig. 1(d), and β -Bi₂O₃ (Fig. 1(e)) was investigated for the oxidation of CH₄ with O₂ as the sole oxidant. There were three main products, i.e., such as formaldehyde (HCHO), carbon monoxide (CO), and carbon dioxide (CO₂). Other products such as CH₃OH were not observed (Fig. S2). Fig. 3(a) shows the HCHO yield as a function of reaction temperature under a CH₄/O₂/N₂ (2/2/6 sccm) flow in the temperature range of 450–600 °C. BiPO₄-DEG selectively gave HCHO with little formation of CO₂. The formation of CO₂ was mainly observed using other bismuth-based catalysts such as BiPO₄-HT, α -Bi₂O₃, and β -Bi₂O₃ (Fig. 3(a) and S2). There was no significant change in the XRD patterns for any of the Bi-based catalysts recovered after CH₄ oxidation (Fig. S3), although some β -Bi₂O₃ was changed to α -Bi₂O₃, which suggests that the catalytic performance is derived from their structures. Although the water vapor plays an important role in the oxidative conversion of CH₄ in some cases,⁶⁷ the presence of water vapor did not enhance the present CH₄ oxidation and HCHO yield/selectivity. The space time yield of BiPO₄-DEG at 600 °C was 0.45 mmol_{HCHO} g⁻¹ h⁻¹ (HCHO selectivity: 40%), and the value and selectivity for HCHO were higher than those for previously-reported Bi-based catalysts such as Bi₂O₃-B₂O₃/SiO₂ (4.3×10⁻² mmol_{HCHO} g⁻¹ h⁻¹, HCHO selectivity: 30%, 550 °C)²³ and Bi-P-O (7.7×10⁻² mmol_{HCHO} g⁻¹ h⁻¹, HCHO selectivity: 4%, 700 °C).²⁶

Next, the catalytic performance of BiPO₄-DEG was compared with that of FePO₄ nanoparticles, which are effective heterogeneous catalysts for the direct oxidation of CH₄ into HCHO.⁴⁴ BiPO₄-DEG functioned as a solid catalyst to efficiently give HCHO at high reaction temperatures compared to FePO₄ (Fig. 3(a)). The HCHO yield of BiPO₄-DEG exceeded that of FePO₄ above 550 °C, while FePO₄ showed higher HCHO yield than BiPO₄-DEG below 550 °C. Notably, a significant difference in the selectivity for HCHO was observed between these two catalysts. Figs 3(b) and 3(c) show the dependence of CH₄ conversion on the reaction temperature and the relationship between selectivity to HCHO and CH₄ conversion, respectively. In the case of FePO₄, the CH₄ conversion increased up to ca. 10% at 600 °C and the selectivity for HCHO was ca. 15–40% in the range of ~2% CH₄ conversion. On the other hand, BiPO₄-DEG showed ca. 40–70% selectivity for HCHO in the same CH₄ conversion region, which suggests that BiPO₄-DEG more selectively promotes the direct oxidation of CH₄ into HCHO than FePO₄. BiPO₄-DEG also exhibited durability without significant change in the selectivity for HCHO (60.6±1.6%) and CO (39.4±1.6%) and CH₄ conversion (0.55±0.02%) at 550 °C for 24 h time-on-stream

as shown in Fig. 3(d). On the other hand, the CO yield gradually decreased from 1.29% (1 h) to 0.52% (12 h) for the CH₄ oxidation at 600 °C (Fig. S4(a)), whereas the HCHO yield was not significantly changed for 12 h and CO₂ was hardly formed in a similar way to the oxidation at 550 °C. Despite such a decrease in the CO yield, the HCHO yield and selectivity after 12 h were 0.74% and 59%, respectively, and higher than those of FePO₄ (0.42% yield and 4% selectivity) at 600 °C. From the XRD pattern for the recovered BiPO₄-DEG catalyst after the reaction at 600 °C (Fig. S4(b)), there was a structural change in the grain sizes for BiPO₄-DEG calculated from the diffraction lines using Scherrer's equation (from 46 to 82 nm for $P_{21/n}$; from 51 to 56 nm for $P_{21/m}$) and the ratio of $P_{21/n}$ to $P_{21/m}$ (from 50/50 to 20/80); thus, the bulk structures of BiPO₄ gradually changed during the CH₄ oxidation at 600 °C in sharp contrast to the reaction at 550 °C.

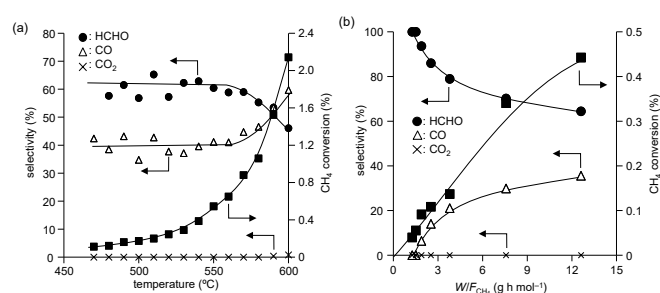


Fig. 4 (a) Product selectivity and CH₄ conversion as function of reaction temperature with O₂ over BiPO₄-DEG. Reaction conditions: BiPO₄-DEG (100 mg), CH₄/O₂/N₂ (2/2/6 sccm). (b) Effect of W/F_{CH_4} on product selectivity and CH₄ conversion. Reaction conditions: BiPO₄-DEG (100 mg), CH₄/O₂/N₂ (38:8:54 molar ratio; total 7.8–78 sccm), reaction temperature (550 °C).

The temperature dependence of CH₄ conversion and product selectivity in CH₄ oxidation with BiPO₄-DEG is shown in Fig. 4(a). HCHO was selectively formed in the low-temperature region (~550 °C), and the CH₄ conversion and selectivity for CO gradually increased with increasing reaction temperature. Fig. 4(b) shows the dependence of the CH₄ conversion and selectivity for each product on the contact time (W/F_{CH_4}). HCHO selectivity decreased with increasing W/F_{CH_4} but the CH₄ conversion and CO selectivity increased, which suggests that HCHO is the primary product and CO is formed by sequential oxidation of HCHO. Such over-oxidation of HCHO into CO and CO₂ is also observed in the direct oxidation of CH₄ with FePO₄.⁴⁴

3.3. Mechanistic studies on direct oxidation of CH₄ into HCHO over BiPO₄

We previously reported that not only the oxidizing ability of metal phosphates but also the surface acid-base properties are key factors in the direct and selective oxidation of CH₄.^{28,43,44} To investigate the oxidizing ability of Bi-based catalysts, H₂-temperature-programmed reduction (H₂-TPR) profiles were measured from 50 to 650 °C (Fig. 5). The reduction of β-Bi₂O₃ started around 250 °C, but the reduction of bismuth phosphates occurred at higher temperatures (from ~350 °C). The H₂

consumption estimated from the H₂-TPR profiles below 550 °C decreased in the order of β-Bi₂O₃ (6.01 mmol g⁻¹) > BiPO₄-DEG (3.53 mmol g⁻¹) > α-Bi₂O₃ (3.13 mmol g⁻¹) > BiPO₄-HT (1.03 mmol g⁻¹) > FePO₄ (0.93 mmol g⁻¹),⁴⁴ which is significantly different from the order of CH₄ conversion at 550 °C (FePO₄ (2.69%) > BiPO₄-DEG (0.54%) > BiPO₄-HT (0.12%) > α-Bi₂O₃ (<0.01%) > β-Bi₂O₃ (0%)) (Fig. S5). In addition, the onset reduction temperature increased in the order of β-Bi₂O₃ (270 °C) < BiPO₄-DEG (320 °C) < α-Bi₂O₃ (350 °C) < FePO₄ (450 °C) < BiPO₄-HT (490 °C), and the order is also inconsistent with the order of reactivity for CH₄ oxidation. A good correlation between H₂ consumption and CH₄ conversion has been reported in the case of iron-based phosphates and oxides.⁴⁴ Thus, the present discrepancy cannot be explained by the reaction mechanism in which lattice oxygen atoms of metal phosphates and oxides are involved in CH₄ oxidation.

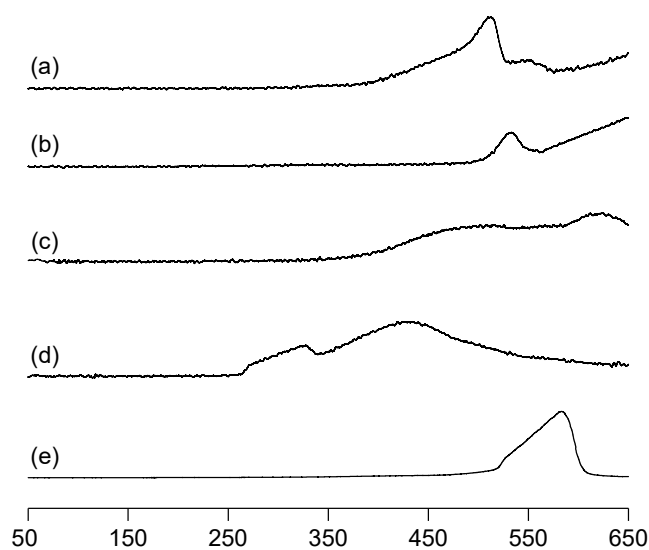


Fig. 5 H₂-TPR profiles for (a) BiPO₄-DEG, (b) BiPO₄-HT, (c) α-Bi₂O₃, (d) β-Bi₂O₃, and (e) FePO₄.

Pulse-reaction experiments for BiPO₄-DEG pretreated in He at 600 °C were conducted to determine the origin of the oxygen atoms incorporated in the oxygenated products (i.e., from the oxygen atoms in BiPO₄ solid or the surface oxygen species generated from gaseous O₂) (Table 2). No formation of oxygenated products was observed in the reaction of only the CH₄ pulse with BiPO₄-DEG in sharp contrast to the FePO₄ nanoparticles that reacted with CH₄ to give C₁ products (HCHO and CO_x) and partially reduced FePO₄₋₆.⁴⁴ On the other hand, HCHO, CO, and CO₂ were formed with selectivities of 44%, 54%, and 2%, respectively, at 0.9% CH₄ conversion when the CH₄ + O₂ pulse (1/1, v/v) was passed through the catalyst bed at 600 °C. The formation of C₂-coupling products such as ethane and ethylene was not observed for both the pulse reaction and catalytic oxidation of CH₄ over BiPO₄-DEG. Oxidative coupling of CH₄ (OCM) typically proceeds under the harsh reaction conditions (>650 °C) to cleave the strong C–H bonds of CH₄, and it is well accepted that the generation of methyl radicals by the solid-catalyst surface with subsequent gas-phase propagation and termination is involved in the OCM mechanism.^{2,4,13} These

results suggest that the surface oxygen species generated from O_2 and $BiPO_4$ likely reacted with CH_4 to yield C_1 products ($HCHO$ and CO_x) without the formation of methyl radicals in the gas-phase. The kinetics of CH_4 oxidation over $BiPO_4$ -DEG at $550\text{ }^\circ\text{C}$ were investigated. Fig. 6(a)–6(c) show the dependence of the reaction rate (CH_4 conversion) on the partial pressures of CH_4 (P_{CH_4}) and O_2 (P_{O_2}), and the catalyst loading of $BiPO_4$ -DEG. A first-order dependence of the reaction rates on P_{CH_4} and catalyst loading was observed (Fig. 6(a) and 6(c)). The dependence of the reaction rate on P_{O_2} exhibited saturation kinetics (Fig. 6(b)), which is consistent with the Langmuir–Hinshelwood mechanism through adsorption (i.e., activation) of O_2 .^{68–71}

Table 2 Pulse reaction experiments on oxidation of CH_4 with $BiPO_4$ -DEG.^a

entry	pulse	CH_4 conversion (%)	yield (%) (selectivity (%))		
			HCHO	CO	CO–
1	CH_4	<0.01	<0.01 (–)	<0.01 (–)	<0.01 (–)
2	$CH_4 + O_2$ (1/1, v/v)	0.93	0.41 (44)	0.50 (54)	0.02 (2)

^a Reaction conditions: $BiPO_4$ -DEG (100 mg), He (20 sccm), pulse volume (1 mL), reaction temperature ($600\text{ }^\circ\text{C}$).

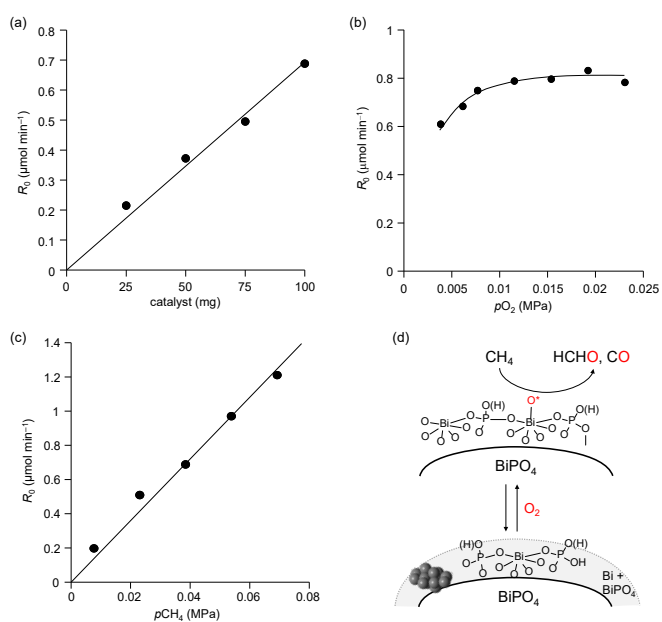


Fig. 6 Effect of (a) catalyst amount and partial pressure of (b) O_2 and (c) CH_4 on reaction rate. Reaction conditions for (a): $BiPO_4$ -DEG (25–100 mg), $CH_4/O_2/N_2$ (5/1/7 sccm; total 13 sccm), reaction temperature ($550\text{ }^\circ\text{C}$). Reaction conditions for (b): $BiPO_4$ -DEG (100 mg), $CH_4/O_2/N_2$ (5/0.5–3/7.5–5 sccm; total 13 sccm), reaction temperature ($550\text{ }^\circ\text{C}$). Reaction conditions for (c): $BiPO_4$ -DEG (100 mg), $CH_4/O_2/N_2$ (1–9/1/11–3 sccm; total 13 sccm), reaction temperature ($550\text{ }^\circ\text{C}$). (d) Proposed reaction mechanism for oxidation of CH_4 with O_2 over $BiPO_4$ -DEG.

XPS measurements were performed to further investigate the surface structures of $BiPO_4$ -DEG. For the XPS Bi 4f spectrum of $BiPO_4$ -DEG at room temperature, a main peak around 159.8

eV (Bi 4f_{7/2}) assignable to Bi^{3+} species in $BiPO_4$ and a slight peak around 155.9 eV of metallic Bi species were observed (Fig. 7(a)).^{72,73} Such formation of metallic Bi species has also been reported for $BiPO_4$ synthesized in ethylene glycol solvent probably due to the weak reducing ability of ethylene glycol.⁴⁸ It has also been reported that the formation of surface oxygen vacancies of $BiPO_4$ leads to the disordered edge of $BiPO_4$ particles observed by TEM analyses.⁵¹ In the case of $BiPO_4$ -DEG, the edge of the nanoparticles become disordered (thickness ~ 1 nm, Fig. 2(d)), which supports the formation of metallic Bi species. The XPS O 1s spectrum of $BiPO_4$ -DEG also showed a peak around 533 eV which corresponds to adsorbed water in addition to the main peak around 531 eV assignable to lattice oxygen of $BiPO_4$.

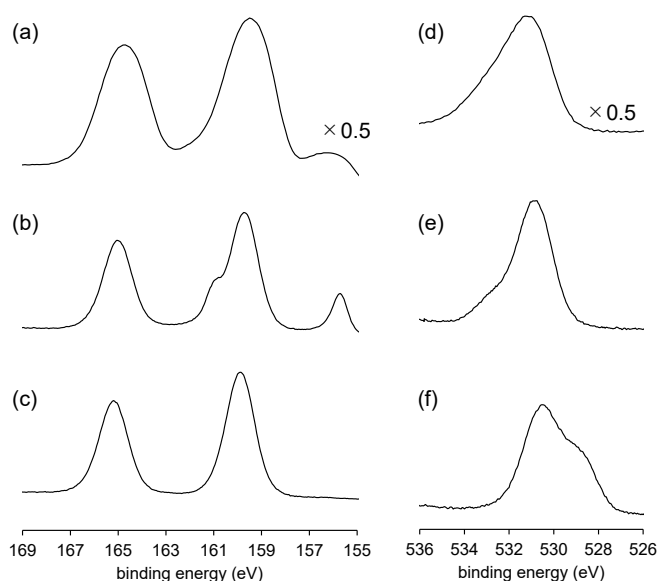


Fig. 7 XPS (a–c) Bi 4f and (d–f) O 1s spectra of $BiPO_4$ -DEG. (a and d) $BiPO_4$ -DEG at room temperature under evacuation, (b and e) $BiPO_4$ -DEG at $550\text{ }^\circ\text{C}$ under evacuation, and (c and f) $BiPO_4$ -DEG at $550\text{ }^\circ\text{C}$ under O_2 (0.1 mbar).

Surface oxygen species are formed on a $CePO_4$ catalyst through the activation of the O_2 molecule assisted by the electric field. Such active oxygen species possibly facilitate the oxidative coupling of the CH_4 reaction even at low temperature. In this case, the surface Lewis acidic Ce sites would play an important role in the activation of O_2 .^{28,43} Therefore, the surface acid properties of the present $BiPO_4$ -DEG catalyst were investigated by IR measurements of samples adsorbed with pyridine and acetone. The IR spectrum for pyridine-adsorbed $BiPO_4$ -DEG showed a band at 1446 cm^{-1} assignable to the pyridine species coordinated to the Lewis acid sites, and no band at 1540 cm^{-1} due to pyridinium ions bonded to the Brønsted acid sites (Fig. 8(a)). The amount of Lewis acid sites was estimated to be $26\text{ }\mu\text{mol g}^{-1}$ from the intensity of the band at 1446 cm^{-1} . The density of surface Bi cations on $BiPO_4$ -DEG was calculated to be 1.6 nm^{-2} from the BET surface area of $BiPO_4$ -DEG and the amounts of Lewis acid sites measured using pyridine-adsorbed IR. This value was comparable to that for

monoclinic CePO_4 nanorods (1.6 nm^{-2}) with monazite-type structure and the calculated value estimated from the main surface structure obtained from HAADF-STEM observation.^{28,29} The IR spectrum of acetone adsorbed on BiPO_4 -DEG (Fig. 8(b)) showed one strong C=O stretching band due to acetone molecules coordinated to Lewis acid sites, with the band position at a lower wavenumber (1683 cm^{-1}) than those for acetone in the gas phase (1731 cm^{-1}), CePO_4 (1699 cm^{-1}), and FePO_4 (1685 cm^{-1}).^{28,43,44} All these results support the presence of uniform surface Lewis acidic Bi species on the BiPO_4 -DEG nanoparticles. Such coordinatively unsaturated sites would be involved in the O_2 activation. In addition, the basicity was also evaluated by IR spectroscopy with adsorbed CHCl_3 and CH_3OH (Fig. 8(c) and 8(d)). The presence of weakly-basic phosphate units on BiPO_4 was confirmed,[‡] which likely contributes to the suppression of complete oxidation to CO_2 in a similar way to the CH_4 oxidation over FePO_4 .⁴⁴

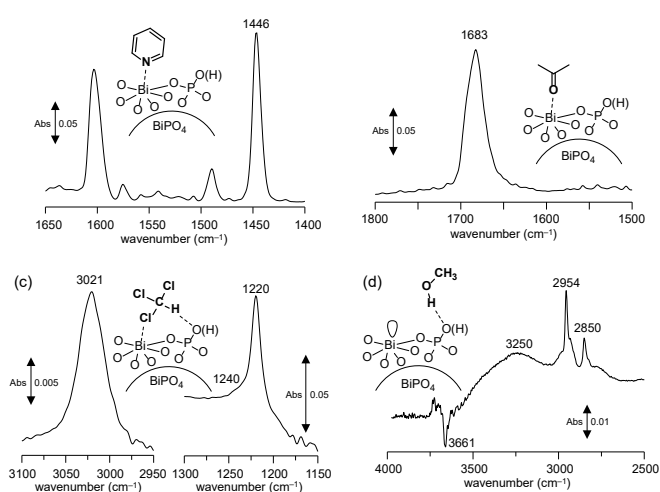


Fig. 8 Difference IR spectra for (a) pyridine-, (b) acetone-, (c) chloroform-, and (d) CH_3OH -adsorbed BiPO_4 -DEG at 25°C .

To obtain information on possible active oxygen species formed on surface Bi sites, an *operando* near-ambient-pressure X-ray photoelectron spectroscopy (NAP-XPS) experiment was conducted under O_2 atmosphere. When BiPO_4 -DEG was exposed to O_2 (0.1 mbar) at 550°C , only the peak corresponding to BiPO_4 was observed in the XPS Bi 4f spectra with the disappearance of the peak of metallic Bi, which suggests reconstruction of the surface structure. The XPS O 1s spectra also changed during the reaction of BiPO_4 -DEG with O_2 . While the main peak around 531 eV assignable to lattice oxygens of BiPO_4 was unchanged, the peak around 533 eV corresponding to adsorbed oxygen atoms disappeared and a new peak around 529 eV appeared upon exposure of O_2 . It has been reported that the peaks due to bismuth oxides are in the range of 528.8–529.9 eV and that the negative shift of O 1s peaks is likely caused by the presence of non-bridging Bi-O species.^{74–78} Thus, the new peak may be caused by surface oxygen species such as Bi-O species generated on BiPO_4 , which possibly react with CH_4 to give HCHO as a primary product. There was no significant difference in the XPS Bi 4f spectra between the fresh and

recovered BiPO_4 -DEG catalysts after the CH_4 oxidation under the conditions in Fig. S6, which suggests that the *in-situ* generated oxygen species observed in the reaction temperature range play an important role in the present CH_4 oxidation.

To further investigate possible involvement of surface active oxygen species on BiPO_4 , density functional theory (DFT) calculations were carried out. Since the surface Bi density of BiPO_4 -DEG was comparable to that of monoclinic CePO_4 nanorods as described above, the monazite-type structure (P_21/n) was used as a model catalyst for the CH_4 oxidation. Surface energy calculations for the (100), (110), and (111) surfaces of BiPO_4 identified that the (100) surface is the most stable one. Furthermore, the DFT-based thermodynamic analysis have shown that the partially oxidized $\text{BiPO}_4(100)$ surface (0.25 monolayer) in which O atom adsorbed on Bi is the stable surface under the reaction environment (see the details in ESI, Fig. S7 and S8). The following two pathways the CH_4 activation were compared: (i) H-abstraction by surface O atom and CH_3 adsorption on PO_4 units, and (ii) H-abstraction by lattice O atom and CH_3 adsorption on PO_4 units. Fig. 9 shows the optimized geometry and the reaction energies for CH_4 activation by these two pathways. The reaction energy (ΔE) is defined as the dissociative adsorption energy of CH_4 . H-abstraction using a surface O atom is an exothermic reaction, since the calculated ΔE is -1.65 eV . On the other hand, H-abstraction by a lattice O atom is an endothermic reaction ($\Delta E = 0.94 \text{ eV}$). Thus, our calculations indicate that the CH_4 activation takes place using surface O atoms, and not lattice O atoms. The surface O atoms are formed from gaseous O_2 in the inlet gas, and therefore CH_4 activation requires the presence of O_2 . This is consistent with the observed reaction rate dependence on P_{O_2} as seen in Fig. 6. In addition to the possible involvement of surface oxygen species generated on BiPO_4 , the weak basicity on BiPO_4 (Fig. 8(c) and 8(d)),[‡] similar to those on FePO_4 and CePO_4 , likely leads to high HCHO selectivity of BiPO_4 -DEG.⁷⁹

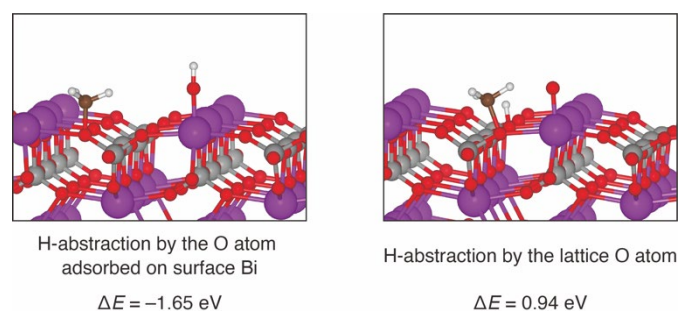


Fig. 9 Optimized structure of the product state of the CH_4 activation on 0.25 ML Bi-oxidized BiPO_4 (100) surface. Two reaction pathways are considered, and their reaction energies (ΔE s) calculated with the DFT are shown.

Conclusions

In summary, bismuth-based phosphate and oxide catalysts were investigated for the oxidation of CH_4 with O_2 as the sole oxidant. Monoclinic BiPO_4 nanoparticles (BiPO_4 -DEG) exhibited

higher catalytic performance for the direct oxidation of CH₄ into HCHO than BiPO₄ synthesized by the hydrothermal method (BiPO₄-HT), α-Bi₂O₃, and β-Bi₂O₃. The lack of correlation between the catalytic activity and oxidizing ability estimated by H₂-TPR and pulse reaction experiments suggested that CH₄ oxidation did not proceed with lattice oxygen supplied from the BiPO₄-DEG solid. On the basis of mechanistic studies including the catalyst effect, kinetics, NAP-XPS, and DFT calculations, the oxidation of CH₄ may proceed at surface oxygen species generated on surface Bi atoms of BiPO₄. IR spectroscopy measurements of BiPO₄-DEG with adsorbed probe molecules indicate the presence of uniform Lewis acid sites and weak basic sites, which possibly activate O₂ and suppress subsequent oxidation into CO₂, respectively. Such a possible O₂ activation mode for BiPO₄-DEG would result in high selective formation of HCHO at high temperatures in sharp contrast to FePO₄ nanoparticles with the redox mechanism.

Author Contributions

A. M. and K. O. designed the experiments, performed the experimental investigation, and conducted data analyses with the help of K.K. A. I. performed the DFT calculations. M. T., C. W., Y. L. performed the NAP-XPS analyses. K. K., A. I., and Y. L. wrote the paper. The draft was reviewed by A. M., A. I., Y. L., M. H. and K. K.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This study was funded in part by a Grant-in-Aid (21H01713) for Scientific Research from the Japan Society for the Promotion of Science (JSPS), and the PRESTO (JPMJPR15S3), CREST (JPMJCR16P3), and A-STEP (JPMJTR20TG) programs of the Japan Science and Technology Agency (JST), and the "Design and Engineering by Joint Inverse Innovation for Materials Architecture" program of the Japan Ministry of Education, Culture, Sports, Science and Technology (MEXT).

Notes and references

‡ The basicity was confirmed by IR spectroscopy with adsorbed CHCl₃ (Fig. 8(c) and 8(d)). The red-shift of the original C–H stretching mode of the CHCl₃ molecule from 3034 cm⁻¹ to 3021 cm⁻¹ indicates the presence of basic sites on the surface.⁷⁴ The band shift (13 cm⁻¹) was larger than that for FePO₄ (~1 cm⁻¹) but lower than that for CePO₄ (26 cm⁻¹); thus, the basicity of BiPO₄ was stronger than that of FePO₄ but weaker than that of CePO₄.^{39,40} In the IR spectrum of BiPO₄-DEG with adsorbed CH₃OH, broad bands between 3000 and 3500 cm⁻¹ appeared with negative ν(O–H) bands, and bands at 2954 and 2850 cm⁻¹ assignable to the asymmetric and symmetric CH₃ stretching modes of molecularly adsorbed CH₃OH, respectively, were observed. All these results are consistent with previous reports for the interaction of probe molecules on metal phosphates with uniform Lewis acid sites and weak base sites.

- D. Saha, H. A. Grappe, A. Chakraborty and G. Orkoulas, *Chem. Rev.*, 2016, **116**, 11436–11499.
- R. Horn and R. Schlögl, *Catal. Lett.*, 2015, **145**, 23–39.
- A. Abdulrasheed, A. A. Jalil, Y. Gambo, M. Ibrahim, H. U. Hambali and M. Y. Shahul Hamid, *Renew. Sust. Energ. Rev.*, 2019, **108**, 175–193.
- C. Hammond, S. Conrad and I. Hermans, *ChemSusChem*, 2012, **5**, 1668–1686.
- K. Otsuka and Y. Wang, *Appl. Catal. A: Gen.*, 2001, **222**, 145–161.
- A. I. Olivos-Suarez, À. Szécsényi, E. J. M. Hensen, J. Ruiz-Martinez, E. A. Pidko and J. Gascon, *ACS Catal.*, 2016, **6**, 2965–2981.
- M. Ravi, M. Ranocchiari and J. A. van Bokhoven, *Angew. Chem. Int. Ed.*, 2017, **56**, 16464–16483.
- A. V. Vekki and S. T. Marakaev, *Russ. J. Appl. Chem.*, 2009, **82**, 521–536.
- A. H. Bagherzadeh Mostaghimi, T. A. Al-Attas, M. G. Kibria and S. Siahrostami, *J. Mater. Chem. A*, 2020, **8**, 15575–15590.
- S. Ogo and Y. Sekine, *Chem. Rec.*, 2017, **17**, 726–738.
- I. Vollmer, I. Yarulina, F. Kapteijn and J. Gascon, *ChemCatChem*, 2018, **11**, 39–52.
- K. Sun, D. M. Ginosar, T. He, Y. Zhang, M. Fan and R. Chen, *Ind. Eng. Chem. Res.*, 2018, **57**, 1768–1789.
- H. Schwarz, *Angew. Chem. Int. Ed.*, 2011, **50**, 10096–10115.
- M. H. Mahyuddin, Y. Shiota and K. Yoshizawa, *Catal. Sci. Technol.*, 2019, **9**, 1744–1768.
- Z. Jin, L. Wang, E. Zuidema, K. Mondal, M. Zhang, J. Zhang, C. Wang, X. Meng, H. Yang, C. Mesters and F.-S. Xiao, *Science*, 2020, **367**, 193–197.
- P. Xiao, Y. Wang, T. Nishitoba, J. N. Kondo and T. Yokoi, *Chem. Commun.*, 2019, **55**, 2896–2899.
- C. Hammond, M. M. Forde, M. H. Ab Rahim, A. Thetford, Q. He, R. L. Jenkins, N. Dimitratos, J. A. Lopez-Sanchez, N. F. Dummer, D. M. Murphy, A. F. Carley, S. H. Taylor, D. J. Willock, E. E. Stangland, J. Kang, H. Hagen, C. J. Kiely and G. J. Hutchings, *Angew. Chem. Int. Ed.*, 2012, **51**, 5129–5133.
- B. E. R. Snyder, M. L. Bols, R. A. Schoonheydt, B. F. Sels and E. I. Solomon, *Chem. Rev.*, 2018, **118**, 2718–2768.
- P. Schwach, M. G. Willinger, A. Trunschke and R. Schlögl, *Angew. Chem. Int. Ed.*, 2013, **52**, 11381–11384.
- J. H. Lunsford, *Angew. Chem. Int. Ed. Engl.*, 1995, **34**, 970–980.
- B. P. C. Hereijgers and B. M. Weckhuysen, *ChemSusChem*, 2009, **2**, 743–748.
- M. Bugnola, R. Carmieli and R. Neumann, *ACS Catal.*, 2018, **8**, 3232–3236.
- K. Otsuka and M. Hatano, *J. Catal.*, 1987, **108**, 252–255.
- K. Harrath, X. Yu, H. Xiao and J. Li, *ACS Catal.*, 2019, **9**, 8903–8909.
- C. Williams, J. H. Carter, N. F. Dummer, Y. K. Chow, D. J. Morgan, S. Yacob, P. Serna, D. J. Willock, R. J. Meyer, S. H. Taylor and G. J. Hutchings, *ACS Catal.*, 2018, **8**, 2567–2576.
- T. Ohno and J. B. Moffat, *Catal. Lett.*, 1992, **16**, 181–190.
- A. V. Annapragada and E. Gulari, *J. Catal.*, 1990, **123**, 130–146.
- A. Sato, S. Ogo, K. Kamata, Y. Takeno, T. Yabe, T. Yamamoto, S. Matsumura, M. Hara and Y. Sekine, *Chem. Commun.*, 2019, **55**, 4019–4022.
- V. Paunović, G. Zichittella, M. Moser, A. P. Amrute and J. Pérez-Ramírez, *Nat. Chem.*, 2016, **8**, 803–809.
- G. Zichittella, V. Paunović, A. P. Amrute and J. Pérez-Ramírez, *ACS Catal.*, 2017, **7**, 1805–1817.
- Y. Wang and K. Otsuka, *J. Catal.*, 1995, **155**, 256–267.
- Y. Wang, X. Wang, Z. Su, Q. Guo, Q. Tang, Q. Zhang and H. Wan, *Catal. Today*, 2004, **93-95**, 155–161.
- G. O. Alptekin, A. M. Herring, D. L. Williamson, T. R. Ohno and R. L. McCormick, *J. Catal.*, 1999, **181**, 104–112.
- Y. Wang and K. Otsuka, *J. Mol. Catal. A: Chem.*, 1996, **111**, 341–356.

- 35 Y. Wang and K. Otsuka, *J. Chem. Soc., Faraday Trans.*, 1995, **91**, 3953–3961.
- 36 V. Gomonaj and H. Toulhoat, *ACS Catal.*, 2018, **8**, 8263–8272.
- 37 J. Baek, B. Rungtaweivoranit, X. Pei, M. Park, S. C. Fakra, Y.-S. Liu, R. Matheu, S. A. Alshmiri, S. Alshehri, C. A. Trickett, G. A. Somorjai and O. M. Yaghi, *J. Am. Chem. Soc.*, 2018, **140**, 18208–18216.
- 38 T. Ikuno, J. Zheng, A. Vjunov, M. Sanchez-Sanchez, M. A. Ortuno, D. R. Pahls, J. L. Fulton, D. M. Camaioni, Z. Li, D. Ray, B. L. Mehdi, N. D. Browning, O. K. Farha, J. T. Hupp, C. J. Cramer, L. Gagliardi and J. A. Lercher, *J. Am. Chem. Soc.*, 2017, **139**, 10294–10301.
- 39 V. Fornés, C. López, H.H. López and A. Martínez, *Appl. Catal. A: Gen.*, 2003, **249**, 345–354.
- 40 H. Launay, S. Loidant, A. Pigamo, J. L. Dubois and J. M. M. Millet, *J. Catal.*, 2007, **246**, 390–398.
- 41 T. Akiyama, R. Sei and S. Takenaka, *Catal. Sci. Technol.*, 2021, **11**, 5273–5281.
- 42 J. Tian, J. Tan, Z. Zhang, P. Han, M. Yin, S. Wan, J. Lin, S. Wang and Y. Wang, *Nat. Commun.*, 2020, **11**, 5693.
- 43 S. Kanai, I. Nagahara, Y. Kita, K. Kamata and M. Hara, *Chem. Sci.*, 2017, **8**, 3146–3153.
- 44 A. Matsuda, H. Tatenno, K. Kamata and M. Hara, *Catal. Sci. Technol.*, 2021, **11**, 6987–6998.
- 45 P. Sprenger, W. Kleist and J.-D. Grunwaldt, *ACS Catal.*, 2017, **7**, 5628–5642.
- 46 W. K. Darkwah, B. B. Adormaa, M. K. C. Sandrine and Y. Ao, *Catal. Sci. Technol.*, 2019, **9**, 546–566.
- 47 C. Pan, J. Xu, Y. Chen and Y. Zhu, *Appl. Catal., B* 2012, **115–116**, 314–319.
- 48 F. Tian, H. Zhao, G. Li, Z. Dai, Y. Liu and R. Chen, *ChemSusChem* 2016, **9**, 1579–1585.
- 49 J. Xu, L. Li, C. Guo, Y. Zhang and W. Meng, *Appl. Catal., B* 2013, **130–131**, 285–292.
- 50 Y. Guo, P. Wang, J. Qian, Y. Ao, C. Wang and J. Hou, *Appl. Catal., B* 2018, **234**, 90–99.
- 51 Y. Lv, Y. Zhu and Y. Zhu, *J. Phys. Chem. C*, 2013, **117**, 18520–18528.
- 52 F. Qiu, L. T. Weng, P. Ruiz and B. Delmon, *Appl. Catal.*, 1989, **47**, 115–123.
- 53 N. Abadzhieva, P. Tzokov, I. Uzunov, V. Minkov, D. Klissurski and V. Rives, *React. Kinet. Catal. Lett.*, 1994, **53**, 413–418.
- 54 M. Ruwet, S. Ceckiewicz and B. Delmon, *Ind. Eng. Chem. Res.*, 1987, **26**, 1981–1983.
- 55 T.-S. Chang, L. Gujia, C.-H. Shin, Y. K. Lee and S.-S. Yun, *Catal. Lett.*, 2000, **68**, 229–234.
- 56 Y. Takita, M. Ninomiya, R. Matsuzaki, H. Wakamatsu, H. Nishiguchi and T. Ishihara, *Phys. Chem. Chem. Phys.*, 1999, **1**, 2367–2372.
- 57 B. Gallace and J. B. Moffat, *J. Catal.*, 1982, **76**, 182.
- 58 F. Pazoki, S. Bagheri, M. Shamsayei, M. J. Nejad and A. Heydari, *Mater. Chem. Phys.*, 2020, **253**, 123327.
- 59 T. Aihara, W. Aoki, S. Kiyohara, Y. Kumagai, K. Kamata and M. Hara, *ACS Appl. Mater. Interfaces*, 2023, **15**, 17957–17968.
- 60 M. Koutani, E. Hayashi, K. Kamata and M. Hara, *J. Am. Chem. Soc.*, 2022, **144**, 14090–14100.
- 61 Y. Yamaguchi, R. Aono, E. Hayashi, K. Kamata and M. Hara, *ACS Appl. Mater. Interfaces*, 2020, **12**, 36004–36013.
- 62 P. E. Blochl, *Phys. Rev. B*, 1994, **50**, 17953–17979.
- 63 J. Sun, A. Ruzsinszky and J. P. Perdew, *Phys. Rev. Lett.*, 2015, **115**, 036402.
- 64 G. Kresse and J. Furthmuller, *Phys. Rev. B*, 1996, **54**, 11169–11186.
- 65 G. Kresse and J. Furthmuller, *Comput. Mater. Sci.*, 1996, **6**, 15–50.
- 66 B. Romero, S. Bruque, M. A. G. Aranda and J. E. Iglesias, *Inorg. Chem.*, 2002, **33**, 1869–1874.
- 67 K. Takanabe and E. Iglesia, *Angew. Chem., Int. Ed.*, 2008, **47**, 7689–7693.
- 68 E. Hayashi, T. Tamura, T. Aihara, K. Kamata and M. Hara, *ACS Appl. Mater. Interfaces*, 2022, **14**, 6528–6537.
- 69 K. Sugahara, K. Kamata, S. Muratsugu and M. Hara, *ACS Omega*, 2017, **2**, 1608–1616.
- 70 S. Kawasaki, K. Kamata and M. Hara, *ChemCatChem*, 2016, **8**, 3247–3253.
- 71 V. D. Makwana, Y. C. Son, A. R. Howell and S. L. Suib, *J. Catal.*, 2002, **210**, 46–52.
- 72 P. Deng, H. Wang, R. Qi, J. Zhu, S. Chen, F. Yang, L. Zhou, K. Qi, H. Liu and B. Y. Xia, *ACS Catal.*, 2020, **10**, 743–750.
- 73 Q. Jing, L. Huang, Q. Li, Y. Song and L. Chen, *J. Mater. Sci.: Mater. Electron.*, 2020, **31**, 20954–20963.
- 74 J. Gong, C. S. Lee, E. J. Kim, J. H. Kim, W. Lee and Y. S. Chang, *ACS Appl. Mater. Interfaces*, 2017, **9**, 28426–28432.
- 75 J. Liu, S. Guo, H. Wu, X. Zhang, J. Li and K. Zhou, *J. Mater. Sci. Technol.*, 2021, **85**, 1–10.
- 76 J. Sun, J. Wen, G. Wu, Z. Zhang, X. Chen, G. Wang and M. Liu, *Adv. Funct. Mater.*, 2020, **30**, 2004108.
- 77 Q. Chen, Y. Wang and H. Wang, *J. Non-Cryst. Solids*, 2018, **481**, 85–93.
- 78 L. N. Elliott, D. Austin, R. A. Bourne, A. Hassanpour, J. Robb, J. L. Edwards, S. Sutcliffe and T. N. Hunter, *Langmuir*, 2023, **39**, 5697–5709.
- 79 T. Komanoya, K. Nakajima, M. Kitano and M. Hara, *J. Phys. Chem. C*, 2015, **119**, 26540–26546.