



**Structural Evolution During Solution-Based Synthesis of  
 $\text{Li}_7\text{P}_3\text{S}_{11}$  Solid Electrolyte by Synchrotron X-ray Total  
Scattering**

Journal:	<i>Journal of Materials Chemistry A</i>
Manuscript ID	TA-ART-04-2023-002326.R1
Article Type:	Paper
Date Submitted by the Author:	28-Jun-2023
Complete List of Authors:	Shao, Bowen; Rensselaer Polytechnic Institute, Mechanical, Aerospace, and Nuclear Engineering Das, Ratnottam; Rensselaer Polytechnic Institute, Department of Mechanical, Aerospace, and Nuclear Engineering Huang, Yonglin; Rensselaer Polytechnic Institute, Mechanical, Aerospace, and Nuclear Engineering Deng, Ruihao; Rensselaer Polytechnic Institute, Department of Mechanical, Aerospace, and Nuclear Engineering Seelman, Sara; Rensselaer Polytechnic Institute, Department of Materials Science and Engineering Han, Fudong; Rensselaer Polytechnic Institute, Department of Mechanical, Aerospace, and Nuclear Engineering

## ARTICLE

## Structural Evolution During Solution-Based Synthesis of $\text{Li}_7\text{P}_3\text{S}_{11}$ Solid Electrolyte by Synchrotron X-ray Total Scattering

Bowen Shao,<sup>a</sup> Ratnottam Das<sup>a</sup>, Yonglin Huang<sup>a</sup>, Ruihao Deng<sup>a</sup>, Sara Seelman<sup>b</sup> and Fudong Han<sup>a\*</sup>

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Solution-based synthesis has emerged as a promising approach for scalable and efficient synthesis of solid electrolytes (SEs). However, the ionic conductivity of solution-synthesized SEs is much lower than that of SEs synthesized by solid state approaches. The structural evolution during the synthesis of SEs is crucial to explaining the decreased ionic conductivities but has not been well understood. Here, we use synchrotron X-ray total scattering combined with pair distribution function (PDF) analysis to understand the structural evolution during annealing of the solution-processed precursor for the synthesis of  $\text{Li}_7\text{P}_3\text{S}_{11}$  SEs. Combining Bragg diffraction and diffuse scattering, X-ray total scattering enables detection of structural information including phase transition and crystallinity. The results show that the formation of  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass-ceramic starts at 230 °C. Increasing the annealing temperature helps to improve the crystallinity, but the degree of crystallization is still lower than 70.3% even after annealing at 290 °C when thermal decomposition of  $\text{Li}_7\text{P}_3\text{S}_{11}$  to  $\text{Li}_4\text{P}_2\text{S}_6$  has occurred. PDF analysis also revealed the existence of acetonitrile used in the solution-based synthesis in the SEs after annealing at high temperatures. The results rationalize the synthesis-property relationship, explain why annealing at 290 °C provides the highest ionic conductivity in the studied temperatures due to an optimal balance for achieving a high crystallinity while suppressing severe decomposition of  $\text{Li}_7\text{P}_3\text{S}_{11}$ , and provide novel insights to develop approaches for synthesizing superior  $\text{Li}_7\text{P}_3\text{S}_{11}$  SEs at a large scale.

### 1. Introduction

The development of novel battery systems has mainly transitioned to solid-state battery (SSB) based concept which is believed to potentially enable safe, high-energy-density, and high-power-density energy storage.<sup>1,2</sup> The past three decades have observed significant progress in developing superionic solid electrolytes (SEs).<sup>3</sup> Lithium thiophosphate-based ionic conductors, including binary  $\text{Li}_2\text{S-P}_2\text{S}_5$  (LPS),<sup>4</sup>  $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$  (LGPS),<sup>5</sup> and  $\text{Li}_6\text{PS}_5\text{Cl}$  (LPSCl)<sup>6</sup>, and their derivatives are being considered very promising SEs due to their high ionic conductivities and excellent mechanical properties.<sup>7</sup> Nevertheless, full commercialization of SSBs is still challenging due to the difficulties in scalable synthesis and processing of SEs.<sup>8</sup> The aspect of upscaling is critical because large amounts of SEs will be needed for producing SSBs on a Gigafactory scale. One of the most explored routes to synthesizing SEs is solid-state reaction which is achieved by mixing solid precursors and applying heat to drive their reaction. Such an approach has been used to fabricate some of the most conductive SEs.<sup>5</sup> To prevent

the release of volatile sulfur species and to eliminate the unwanted reactions with the vessels and ambient air, solid-state reaction is typically done in an evacuated quartz ampoule. Another widely used approach for SE synthesis is the mechanochemical method (often mentioned as “ball-milling”) which takes advantage of the influence of mechanical energy in chemical transformation.<sup>9</sup> While these approaches are practical for laboratory-scale material discovery and design, both synthetic routes face serious challenges in upscaling. Solid-state reaction involves heating to high temperatures and therefore is an energy-intensive process. The use of quartz ampoules significantly limits the yield (to the order of grams per batch). Mechanochemical synthesis is usually done at room temperature, but to ensure the completion of the reaction, the synthesis is typically performed over a long period (8-50 hours) in a lab-scale ball-milling jar (~50 mL),<sup>10,11</sup> and it is not unreasonable to expect that a longer time will be needed if a large ball-milling jar is used for industrial production.

Solution-based synthesis of SEs has recently become an essential field of scientific research due to its great potential for upscaling.<sup>12-14</sup> Solution-based synthesis of lithium-thiophosphate based SEs is typically achieved by the reaction of  $\text{Li}_2\text{S}$  with  $\text{P}_2\text{S}_5$  at varied molar ratios in organic solvent(s) such as tetrahydrofuran (THF), acetonitrile (ACN), and ethyl acetate (EA), with the possible addition of extra  $\text{Li}_2\text{S}$  and lithium halides for more complex compositions.<sup>15-17</sup> Full dissolution of the precursors may occur in some solvents, but in most cases, the reaction proceeds when the precursors are only partially

<sup>a</sup> Department of Mechanical, Aerospace and Nuclear Engineering, Rensselaer Polytechnic Institute, Troy, NY, USA 12180.

<sup>b</sup> Department of Materials Science and Engineering, Rensselaer Polytechnic Institute, Troy, NY, USA 12180.

\* Corresponding author. Email: hanf2@rpi.edu

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x

dissolved. The desired SEs are obtained after solvent removal and possible heat treatment(s). The particle size of SEs synthesized by solution-based approach is much smaller than that synthesized by solid-state and mechanochemical syntheses,<sup>15</sup> and this will help achieve great contact with electrode active materials. The synthesis is typically performed at relatively low temperatures and therefore is energy-efficient. The low vapor pressure of sulfur species also enables solvent-based synthesis to be done in a glass container. Moreover, this approach allows for far more intimate contact between the reactants even when only partial dissolution occurs, thus providing access for efficient synthesis and upscaling. In addition to the upscaling of SE synthesis, the solution-based approach also has distinct advantages for the post-processing of SEs for SSB fabrication, i.e., for scalable processing of SE materials into electrolyte membranes and mixing of SE materials, electrode active materials, and electronically conductive additives to fabricate electrode sheets.<sup>18,19</sup>


Despite the many benefits of solution-based synthesis, the ionic conductivity of thiophosphate-based SEs synthesized by solution-based approaches are much lower than that of SEs synthesized by solid-state synthesis or mechanochemical approaches, as shown in **Figure S1**. A wide spread of ionic conductivities over a few orders of magnitude can also be observed for the solution-synthesized SEs with identical compositions (**Figure S1**).<sup>16,20–24</sup> Multiple reasons have been reported to explain the low ionic conductivity of solution-synthesized SEs. Yamamoto et al. reported that the existence of residual  $\text{Li}_2\text{S}$  due to incomplete reaction can decrease ionic conductivity.<sup>25,26</sup> Although direct precipitation of the final SE from the solution is desired, the obtained precipitates of the liquid-phase reaction are generally a co-crystallized complex of lithium thiophosphate and the solvent used, i.e., crystalline  $\text{Li}_3\text{PS}_4$ -solvent complex. Subsequent heat treatment is always needed to remove the solvent in the crystalline phase. While the solvent removal process is usually done at a temperature much higher than the boiling point, solvent can remain in the solids and the remaining solvent<sup>27</sup> or its carbonization product<sup>28</sup> after further annealing can also lower the conductivity. In addition, many thiophosphate-based SEs are essentially glass-ceramic materials that contain both crystalline and amorphous phases.<sup>29,30</sup> It has been well known that crystallinity plays a very important role in ionic transport properties of thiophosphate-based SEs. For  $\text{Li}_7\text{P}_3\text{S}_{11}$ , higher crystallinity will lead to higher conductivity,<sup>31</sup> whereas for  $\text{Li}_3\text{PS}_4$ , an increase in crystallinity has been reported to decrease its conductivity.<sup>32</sup> The variation in the crystallinity of the synthesized SE can also be one reason for the decreased conductivity. In addition, the synthesis of some SEs (e.g.,  $\text{Li}_7\text{P}_3\text{S}_{11}$ ) will require additional annealing at a high temperature to further drive the solid-state reaction and

increase the crystallinity, but prolonged annealing at high temperatures may also lead to decomposition of SE to poorly conductive phases.<sup>31,33</sup> Nevertheless, a concrete reason for the decrease in ionic conductivity for solution-synthesized SEs has not been established, although the dominant reason can be different for different thiophosphate SEs.

A comprehensive understanding of the structural evolution of SEs during solution-based synthesis is important to understand the synthesis-property relation but has not been achieved thus far due to the challenges in characterizing the multi-component materials with both amorphous and crystalline structure during the synthesis process. X-ray diffraction (XRD) has been mainly used as the tool to study the structural evolution during synthetic heat treatment,<sup>15,16</sup> but no details on the crystallinity of the sample can be determined. The crystallite size of the SE glass-ceramic synthesized by solution-based method is around tens of nanometers,<sup>15</sup> leading to a rather broad peak which can be difficult for detailed analysis. Raman spectra was also used to reveal the local structure of P-S polyhedral in solution-synthesized SEs<sup>16</sup>, but this surface-specific technique faces challenges in detecting samples in the deep region such as  $\text{Li}_2\text{S}$  core inside a SE shell.<sup>25</sup>


Here, we report the structural evolution of  $\text{Li}_7\text{P}_3\text{S}_{11}$  solid electrolyte during annealing of a solution-processed precursor using synchrotron X-ray total scattering and pair distribution function (PDF) analysis.  $\text{Li}_7\text{P}_3\text{S}_{11}$  was studied because it exhibits one of the highest ionic conductivities (17 mS/cm at room temperature) among all thiophosphate SEs.<sup>15</sup> The utilization of PDF, which takes into account both Bragg scattering and diffuse scattering enables detection of the structural information, including crystal structure, atomic distances, coordination number, disorder, and size of a particle or coherent domain.<sup>34–36</sup> These unique capabilities make PDF very effective in understanding the structure of a multi-component system consisting of both crystalline and amorphous phases. Several previous reports have used PDF to study the local structure of  $\text{Li}_3\text{PS}_4$  during solution synthesis<sup>25–27,37</sup>. However, to our knowledge, no prior study has been reported on PDF study of the structural evolution of  $\text{Li}_7\text{P}_3\text{S}_{11}$ , which exhibits a much higher ionic conductivity than  $\text{Li}_3\text{PS}_4$  and involves more complicated processes (decomplex, solid-state reaction, crystallization, and decomposition) during synthesis. The structural information revealed from PDF is correlated with the ionic conductivity of SEs annealed at different temperatures. The analysis sheds new light on the principal synthesis-structure-property relationships of  $\text{Li}_7\text{P}_3\text{S}_{11}$  through solution synthesis and helps to rationalize precise and scalable synthesis of superionic conductive SEs.

## ARTICLE

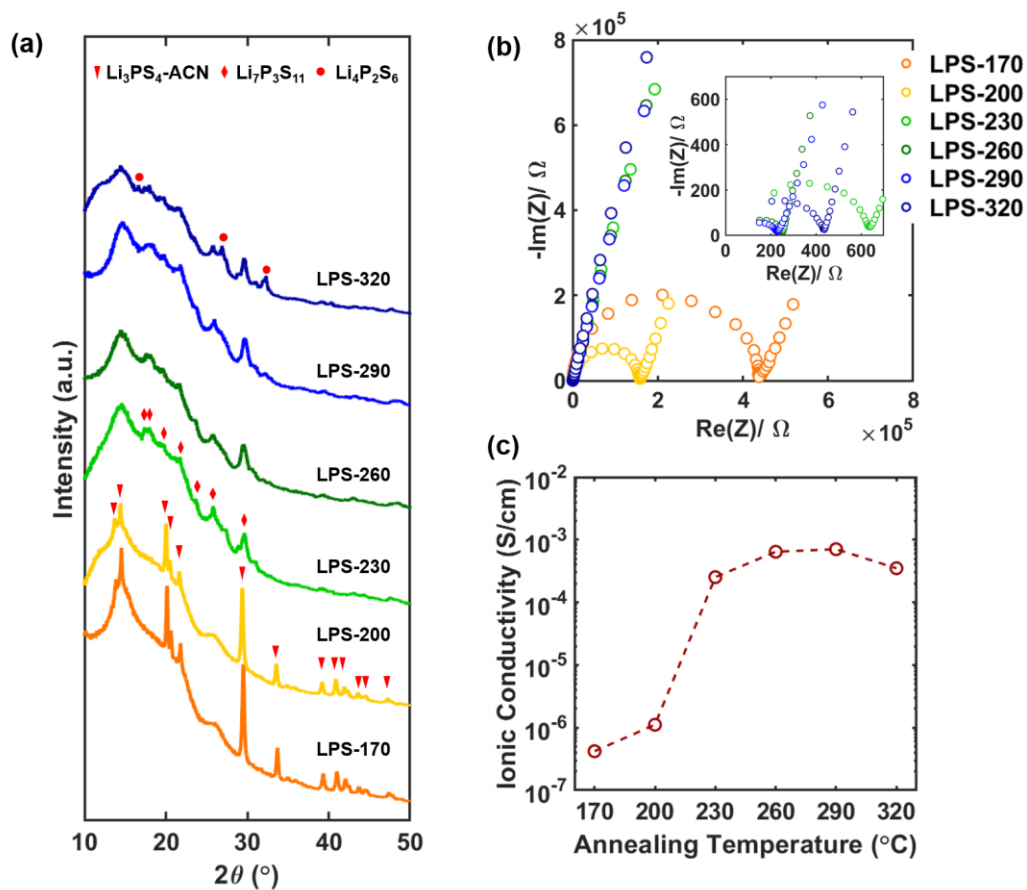

**Figure 1.** (a) Lab X-ray diffraction patterns of SEs synthesized after annealing at different temperatures. (b) Impedance plots of SEs with stainless steel blocking electrodes measured at room temperature. The impedance measurement was performed from 7 MHz to 10 mHz. (c) Room temperature ionic conductivity of SEs synthesized after annealing at different temperatures.

## ARTICLE

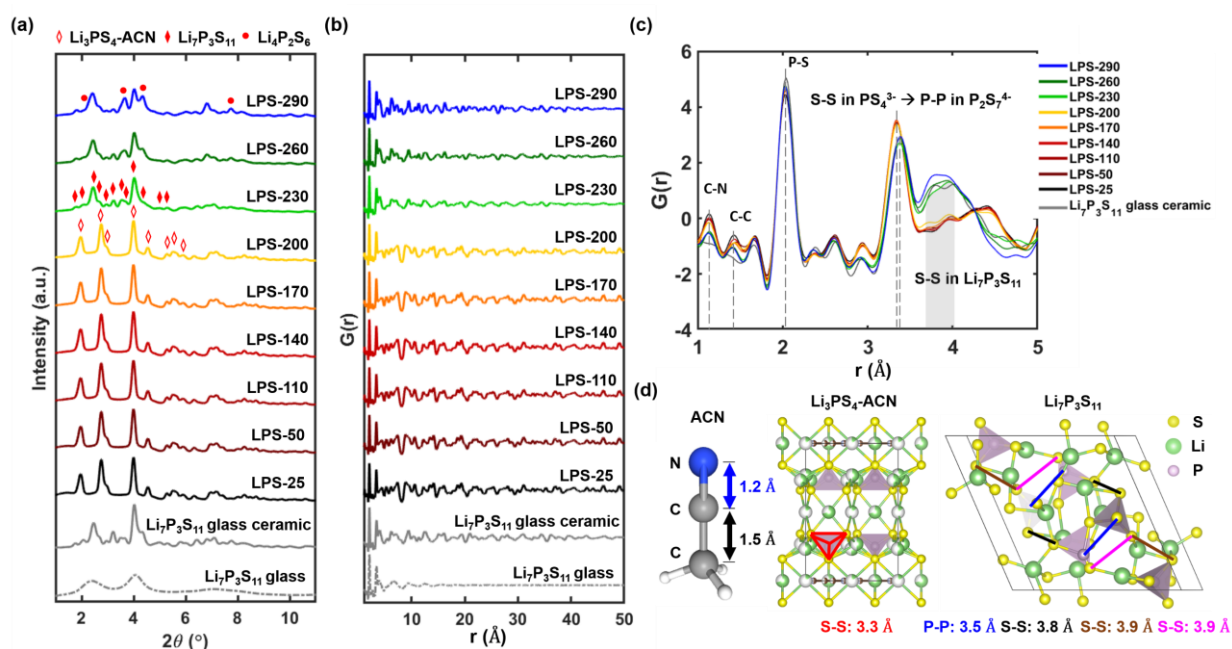

**Figure 2.** (a) Synchrotron diffraction Bragg data of SEs after annealing at different temperatures. The Bragg data of  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass and glass-ceramic synthesized by ball milling method are also provided for comparison. Reduced pair distribution functions,  $G(r)$ , of SEs after annealing at different temperatures in the range of  $1 \text{ \AA} < r < 50 \text{ \AA}$  (b) and in the range of  $1 \text{ \AA} < r < 5 \text{ \AA}$  (c). The dash line in (b) shows the evolution of the peak at about  $3.8 \text{ \AA}$ . (d) Structures of ACN,  $\text{Li}_3\text{PS}_4\text{-ACN}$ , and  $\text{Li}_7\text{P}_3\text{S}_{11}$  with several characteristic bond lengths.

## 2. Results and discussion


### 2.1 Lab X-ray Diffraction and Ionic Conductivity Measurement

To prepare the precursor for the synthesis of  $\text{Li}_7\text{P}_3\text{S}_{11}$ ,  $\text{Li}_2\text{S}$ , and  $\text{P}_2\text{S}_5$  with a molar ratio of 7:3 was mixed in ACN at  $50 \text{ }^\circ\text{C}$  for 3 days and the solvent was then removed by drying under vacuum.<sup>16</sup> The precursor was then annealed at different temperatures from 170 to  $320 \text{ }^\circ\text{C}$  for 1 hour under Argon to synthesize  $\text{Li}_7\text{P}_3\text{S}_{11}$  SEs. The synthesized SEs were denoted as LPS-170, LPS-200, LPS-230, LPS-260, LPS-290, and LPS-320 based on the annealing temperature. **Figure 1a** shows the lab XRD pattern of the synthesized SEs. The peaks for LPS-170 and LPS-200 can be well attributed to  $\text{Li}_3\text{PS}_4\text{-ACN}$  crystalline complex.<sup>38</sup> The existence of  $\text{Li}_3\text{PS}_4\text{-ACN}$  in LPS-170 and LPS-200 is also supported by the Raman spectra (**Figure S2**) which shows a strong peak at  $429 \text{ cm}^{-1}$ , corresponding to  $\text{PS}_4^{3-}$ , and three bands at  $2927 \text{ cm}^{-1}$ ,  $2265 \text{ cm}^{-1}$  and  $366 \text{ cm}^{-1}$  corresponding to the symmetric C-H stretch vibrations,  $\text{C}\equiv\text{N}$  stretching and  $\text{C}-\text{C}\equiv\text{N}$  bending of ACN, respectively. The formation of  $\text{Li}_7\text{P}_3\text{S}_{11}$  starts after annealing at  $230 \text{ }^\circ\text{C}$ . A large decrease in the peak intensity can be

observed for the sample annealed at  $230 \text{ }^\circ\text{C}$  and higher temperatures, implying a decrease of the crystallinity and the formation of glass-ceramic SEs. The formation of  $\text{Li}_4\text{P}_2\text{S}_6$  can be clearly observed for samples annealed at 290 and  $320 \text{ }^\circ\text{C}$  due to the decomposition of  $\text{Li}_7\text{P}_3\text{S}_{11}$ . The formation of  $\text{Li}_7\text{P}_3\text{S}_{11}$  at  $230 \text{ }^\circ\text{C}$  and its decomposition to  $\text{Li}_4\text{P}_2\text{S}_6$  at higher temperatures are also supported by the Raman spectra (**Figure S2**). **Figure 1b** shows the impedance plot of SEs measured using two stainless steel blocking electrodes. The semicircle corresponds to the bulk and grain boundary resistance. The calculated ionic conductivity as a function of annealing temperature is shown in **Figure 1c**. A sharp increase in the ionic conductivity can be observed after annealing  $230 \text{ }^\circ\text{C}$  ( $0.25 \text{ mS/cm}$ ). The ionic conductivity increases as the annealing temperature increases, reaches the maximum for LPS-290 ( $0.70 \text{ mS/cm}$ ), and then decreases to  $0.35 \text{ mS/cm}$  for SE annealed at  $320 \text{ }^\circ\text{C}$ . The maximum ionic conductivity of LPS-290 is still about one order of magnitude lower than the  $\text{Li}_7\text{P}_3\text{S}_{11}$  prepared by mechanochemical method. It has been well known that the ionic conductivity of  $\text{Li}_7\text{P}_3\text{S}_{11}$  increases with crystallinity, and the decomposition product  $\text{Li}_4\text{P}_2\text{S}_6$  is a poor ionic conductor.<sup>31,39</sup> It should be noted that no apparent changes in the morphology and

particle size can be observed for SEs annealed at different temperatures (**Figure S3**), and therefore the evolution in the ionic conductivity is mainly due to the structural evolution in the bulk electrolyte rather than surface or particle boundaries. Correlating with the XRD results, the sharp increase in the ionic conductivity of LPS-230 is due to the formation of crystallites of superionic  $\text{Li}_7\text{P}_3\text{S}_{11}$ . Increasing annealing temperature is expected to increase crystallinity, thus leading to improved ionic conductivity, but annealing at a very high temperature (320 °C) will lead to the formation of poorly conductive  $\text{Li}_4\text{P}_2\text{S}_6$ . It should be noted that the

maximum ionic conductivity was achieved for the SE annealed at 290 °C where apparent decomposition occurs. The results lead to an important question for further improving the ionic conductivity of solution-synthesized SE: *how to improve the crystallinity of  $\text{Li}_7\text{P}_3\text{S}_{11}$  without causing decomposition?* The results also suggest that crystallization to the desired  $\text{Li}_7\text{P}_3\text{S}_{11}$  phase (usually determined by lab XRD) is overly simplistic to describe the success of synthesis. More careful and quantitative analysis on the crystallinity of the obtained SE should be done to fully understand the synthesis-property relation for identifying the optimum synthetic condition.

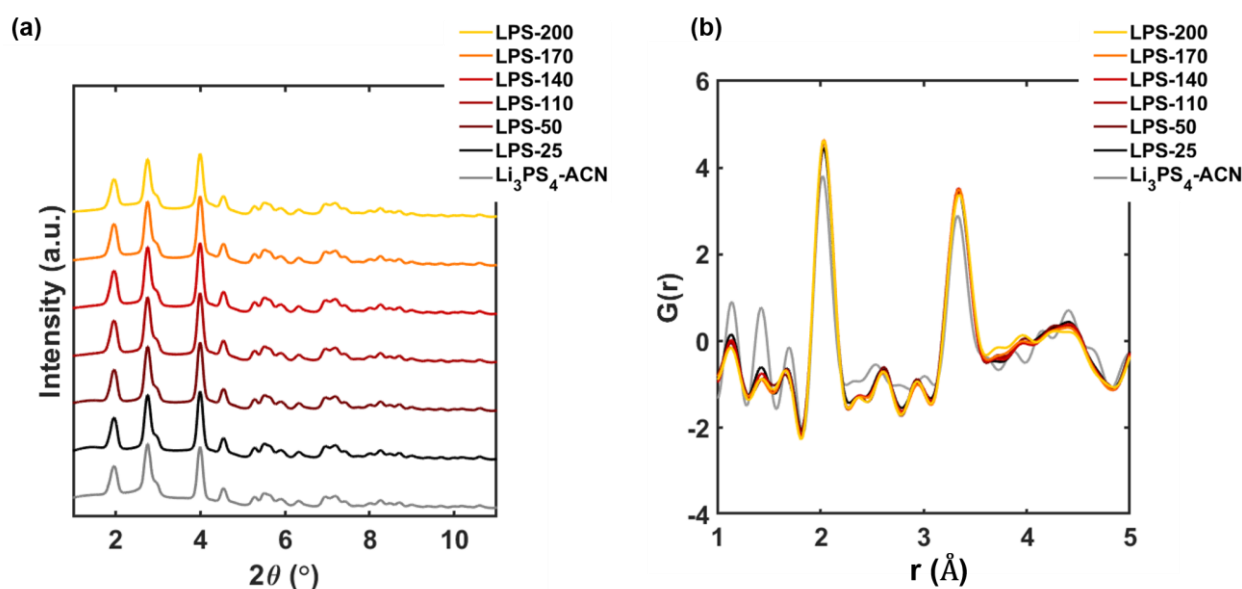

**Figure 3.** Synchrotron diffraction Bragg data (a) and reduced PDFs (b) of SEs after annealing at temperatures below 200 °C. The data of pure  $\text{Li}_3\text{PS}_4$ -ACN crystalline complex is also provided for comparison.

## 2.2 Ex-situ Diffraction and Reduced PDFs from Synchrotron X-ray Total Scattering

We use synchrotron X-ray total scattering to better understand the structural evolution of SEs after annealing at different temperatures. Combining both Bragg scattering and diffuse scattering, total scattering technique can not only provide information on the crystal structure that can be directly correlated to different thiophosphate phases but also reveal the local structure, through PDF analysis, to understand the degree of the crystallization. **Figure 2a** shows the Bragg data from the total scattering measurement. The diffraction results agree very well with the lab XRD data (**Figure 1a**). The conversion between  $\text{Li}_3\text{PS}_4$ -ACN and  $\text{Li}_7\text{P}_3\text{S}_{11}$  occurs at 230 °C, and decomposition of  $\text{Li}_7\text{P}_3\text{S}_{11}$  to  $\text{Li}_4\text{P}_2\text{S}_6$  can be clearly observed after annealing at 290 °C. A decrease in the peak intensity can also be observed after  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass ceramic has been formed after 230 °C.

We then analyze the reduced PDF of SEs after annealing at different temperatures. The reduced PDFs in the range of  $1 \text{ \AA} < r < 50 \text{ \AA}$  (**Figure 2b**) show very similar profiles for SEs annealed at lower temperatures from 25 to 200 °C. Apparent changes in the reduced PDF profile can be observed after 230 °C and the profile looks similar to that of the  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass-ceramic, suggesting the formation of  $\text{Li}_7\text{P}_3\text{S}_{11}$  occurs at 230 °C. The decrease in long-range ordering in the high  $r$  range ( $> 40 \text{ \AA}$ ) can also be observed at 230 °C, consistent with a decrease in crystallinity as  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass-ceramic forms.

The reduced PDFs in a lower range of  $1 \text{ \AA} < r < 5 \text{ \AA}$  are provided in **Figure 2c** to reveal more information on the local structure evolution after annealing at different temperatures. All samples show a main peak at 2 Å which can be attributed to the P-S bond in  $\text{PS}_4^{4-}$  tetrahedra. While different P-S polyhedra are present in  $\text{Li}_3\text{PS}_4$ -ACN ( $\text{PS}_4^{4-}$ ), amorphous  $\text{Li}_7\text{P}_3\text{S}_{11}$  ( $\text{PS}_4^{4-}$ ,  $\text{P}_2\text{S}_7^{2-}$ , and  $\text{P}_2\text{S}_6^{4-}$ ) and crystalline  $\text{Li}_7\text{P}_3\text{S}_{11}$  ( $\text{PS}_4^{4-}$  and  $\text{P}_2\text{S}_7^{2-}$ ), the two main structural units  $\text{PS}_4^{4-}$ ,  $\text{P}_2\text{S}_7^{2-}$  have very similar short-range structure because  $\text{P}_2\text{S}_7^{2-}$  is

essentially two corner-sharing  $\text{PS}_4^{4-}$ .<sup>14</sup> Another important feature is the peak at 3.4 Å shifts to a slightly higher  $r$  value as the annealing temperature increases from 200 °C (yellow) to 230 °C (green), and we believe the shift is caused by changes in the coordination from S-S (3.3 Å) in  $\text{PS}_4^{4-}$  of  $\text{Li}_3\text{PS}_4$ -ACN to P-P (3.5 Å) in the  $\text{P}_2\text{S}_7^{2-}$  in  $\text{Li}_7\text{P}_3\text{S}_{11}$  (Figure 2d). A more predominant feature that can be observed is the appearance of a broad peak from 3.8 Å to 4.0 Å for LPS-230, LPS-260, and LPS-290. The broad peak is present in the  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass-ceramic, and the appearance of this broad peak is attributed to the formation of multiple S-S bonds in  $\text{Li}_7\text{P}_3\text{S}_{11}$  with a bond length at around 3.8 or 3.9 Å (Figure 2d). All of these results suggest that the transformation from  $\text{Li}_3\text{PS}_4$ -ACN to  $\text{Li}_7\text{P}_3\text{S}_{11}$  occurs at 230 °C which is consistent with the diffraction results (Figures 1a and 2a).

It should also be noted that two peaks at 1.2 Å and 1.4 Å appeared in the reduced PDFs for SEs annealed at all temperatures. Those two peaks cannot be observed in the synchrotron X-ray and neutron PDFs of  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass and glass-ceramic synthesized by ball-milling method (Figure S4) and are attributed to the C-N and C-C bonds respectively based on the bond lengths of ACN shown in Figure 2d. While the existence of local structure of ACN is expected at temperatures below 200 °C because the major phase is  $\text{Li}_3\text{PS}_4$ -ACN crystalline complex, it is quite surprising to see that ACN remains in the SE annealed at a very high temperature of 290 °C which is much higher than the boiling point of ACN (82 °C), although the intensity of the peaks decrease as the annealing temperature increases. Overall, the local structure analysis confirms that the transition from  $\text{Li}_3\text{PS}_4$ -ACN to  $\text{Li}_7\text{P}_3\text{S}_{11}$  starts from 230 °C. More importantly, it also shows the existence of ACN even for SEs that are annealed at high temperatures. The existence of solvent can have a large influence on the ionic transport properties, but this factor has not been considered in previous literature. It should be noted that the existence of ACN is not observable in the Raman spectra of SE annealed at temperatures higher than 230 °C because Raman, as a surface specific technique, cannot provide structural information in the bulk SEs, highlighting the unique advantage of the synchrotron total scattering for the current research.

### 2.3 Structural Evolution Before $\text{Li}_7\text{P}_3\text{S}_{11}$ Formation

To further understand the synthetic pathway, we then separately discuss the structural evolution before and after the transition temperature. For the SEs annealed at temperatures lower than 200 °C, the Bragg data (Figure 3a) agree very well with that of pure  $\text{Li}_3\text{PS}_4$ -ACN crystalline complex which is separately synthesized by solution method with a molar ratio of  $\text{Li}_2\text{S}$  to  $\text{P}_2\text{S}_5$  being 3:1. No other crystalline phases can be observed. In contrast, the reduced PDF profiles of SEs (Figure 3b) are quite different from that of  $\text{Li}_3\text{PS}_4$ -ACN. The intensities of the peaks corresponding to ACN (at 1.2 Å and 1.4 Å) are much lower in the SEs than in pure  $\text{Li}_3\text{PS}_4$ -CAN while the intensities of the peaks at ~2.1 Å and ~3.4 Å, which exist in typical LPS thiophosphate, are much higher in the SEs than in pure  $\text{Li}_3\text{PS}_4$ -ACN. The results suggest that an additional component that is amorphous in nature and without ACN also exists in the solution processed precursor. Wang et al<sup>16</sup> reported that the composition of the amorphous component is  $\text{Li}_2\text{S}$ - $\text{P}_2\text{S}_5$  with a molar

ratio of 1:1. This amorphous component, which is presumably the product dried from the supernatant,<sup>16</sup> is critical for the successful synthesis because it will react with  $\text{Li}_3\text{PS}_4$ -ACN to form  $\text{Li}_7\text{P}_3\text{S}_{11}$ . Our Raman spectra of LPS-170 and LPS-230 suggest that the local structure of P in the amorphous  $\text{Li}_2\text{S}$ - $\text{P}_2\text{S}_5$  mainly contains  $\text{P}_2\text{S}_6^{4-}$  and  $\text{P}_2\text{S}_7^{2-}$  (Figure S2). More careful characterization of the product dried from the supernatant should be done in the future to understand the local structure of the amorphous component in the precursor. Although the intensities for the peaks corresponding to ACN gradually decrease as the annealing temperature increases, no apparent evidence can be observed for the formation of crystalline and amorphous  $\text{Li}_3\text{PS}_4$  for LPS-200 because no new crystalline phases can be observed from the diffraction data (Figure 3a) and the decomplex from  $\text{Li}_3\text{PS}_4$ -ACN to amorphous  $\text{Li}_3\text{PS}_4$  will lead to apparent changes in the reduced PDFs (Figure S5). Therefore, no apparent decomplex reaction occurs within this temperature range.

### 2.4 Structural Evolution After $\text{Li}_7\text{P}_3\text{S}_{11}$ Formation

Figures 4a-c show the diffraction Bragg data from the total scattering measurement. The reflection peaks for LPS-230 (Figure 4a) could be attributed to single-phase  $\text{Li}_7\text{P}_3\text{S}_{11}$ . The reflection peaks for SEs annealed at 260 °C (Figure 4b) and 290 °C (Figure 4c) can be refined with a mixture of  $\text{Li}_7\text{P}_3\text{S}_{11}$  and  $\text{Li}_4\text{P}_2\text{S}_6$  phases, indicating the decomposition of  $\text{Li}_7\text{P}_3\text{S}_{11}$  at higher temperatures. The phase fraction of  $\text{Li}_4\text{P}_2\text{S}_6$  is also determined to increase from 13.35% to 32.15% as temperature increases from 260 °C (Figure 4b) to 290 °C (Figure 4c). To quantitatively understand the evolution of crystallinity as the temperature increases, we used difference PDF method<sup>40,41</sup> where the reduced PDFs of SEs annealed at different temperatures,  $G(r)_{\text{experimental}}$ , were fitted by a linear combination of the reduced PDF of ball-milled  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass ( $G(r)_{\text{glass}}$ ) and the reduced PDF of  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass-ceramic ( $G(r)_{\text{glass-ceramic}}$ ) by the following equation:

$$G(r)_{\text{experimental}} = (1 - x)G(r)_{\text{glass}} + xG(r)_{\text{glass-ceramic}}$$

where  $x$  can be used as a quantitative parameter to understand the crystallinity of the samples. Assuming the ball-milled  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass is amorphous (Figure 2b), because the  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass-ceramic synthesized by annealing ball-milled  $\text{Li}_7\text{P}_3\text{S}_{11}$  at 260 °C for 12 hours is fully crystalline<sup>31,33</sup>,  $x$  can only be used as the upper bound for the crystallinity. Figures 4d-f show the observed, fitted and difference profiles of SEs annealed at different temperatures. Excellent fitting can be observed for LPS-230 (Figure 4d). Combining the diffraction data (Figure 4a) and reduced PDF (Figure 4d), the major components for LPS are crystalline and amorphous  $\text{Li}_7\text{P}_3\text{S}_{11}$ . The absence of  $\text{Li}_3\text{PS}_4$ -ACN, amorphous  $\text{Li}_3\text{PS}_4$ , or crystalline  $\text{Li}_3\text{PS}_4$  in LPS-230 exclude the possibility of identifying the mechanism of  $\text{Li}_3\text{PS}_4$ -ACN to  $\text{Li}_7\text{P}_3\text{S}_{11}$  conversion (e.g., decomplex from  $\text{Li}_3\text{PS}_4$ -ACN to  $\text{Li}_3\text{PS}_4$  followed by solid-state reaction between  $\text{Li}_3\text{PS}_4$  and amorphous precursor or direct reaction between  $\text{Li}_3\text{PS}_4$ -ACN and the amorphous precursor).


The R-factor for the linear combination fitting increases as annealing temperature increases to 260 °C (**Figure 4a**) and 290 °C due to the existence of  $\text{Li}_4\text{P}_2\text{S}_6$  phase in the samples. The existence of  $\text{Li}_4\text{P}_2\text{S}_6$  in LPS-260 and LPS-290 is also supported by comparing the residual profile with the calculated PDF of  $\text{Li}_4\text{P}_2\text{S}_6$  (**Figures 4g-4i**), as a reasonably good agreement can be observed between the residual profile of LPS-290 and  $\text{Li}_4\text{P}_2\text{S}_6$  (**Figure 4i**). The linear combination fitting allows determination of the phase fraction of  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass-ceramic in the SEs annealed at different temperatures (**Figure 4j**). The result shows that the fraction of  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass-ceramic increases from 57.7% to 70.3% as the annealing temperature increases from 230 to 290 °C. The results suggest that the crystallinity of  $\text{Li}_7\text{P}_3\text{S}_{11}$  in the SE is expectedly increased as the annealing temperature increases. However, since this fraction can only be considered as an upper bound of crystallinity, even annealing at 290 °C, where decomposition already occurs, cannot lead to a fully crystalline  $\text{Li}_7\text{P}_3\text{S}_{11}$  in the SE.

Correlating the structural information with the ionic conductivity of SEs annealed at different temperatures, we are able to get a better understanding on the synthesis-structure-property relationship. As shown in **Figure 5**, at temperatures lower than 200 °C, the removal of ACN from  $\text{Li}_3\text{PS}_4$ -ACN complex cannot occur, leading to the co-existence of poorly

conductive crystalline  $\text{Li}_3\text{PS}_4$ -ACN complex and amorphous  $\text{Li}_2\text{S}$ - $\text{P}_2\text{S}_5$  precursor dried from the supernatant. Increasing the annealing temperature to 230 °C is sufficient for the removal of ACN and the solid-state reaction of the precursors to form  $\text{Li}_7\text{P}_3\text{S}_{11}$ , although based on the current ex-situ study we are unable to tell whether the solvent removal process occurs prior to or simultaneously with the solid-state reaction. The formation of  $\text{Li}_7\text{P}_3\text{S}_{11}$  at 230 °C explains the sharp increase in the ionic conductivity from 200 °C ( $1.1 \times 10^{-6}$  S/cm) to 230 °C ( $2.5 \times 10^{-4}$  S/cm), but the ionic conductivity of  $\text{Li}_7\text{P}_3\text{S}_{11}$  is still limited due to the low crystallinity (<57.7%), as it has been well known that for  $\text{Li}_7\text{P}_3\text{S}_{11}$  the ionic conductivity increases with the increase in crystallinity.<sup>31,33</sup> Further increase in the annealing temperature can improve crystallinity, which can improve the ionic conductivity, but also lead to the formation of poorly conductive  $\text{Li}_4\text{P}_2\text{S}_6$  due to decomposition of  $\text{Li}_7\text{P}_3\text{S}_{11}$ . Therefore, two competing mechanisms exist during high-temperature annealing. At 260 and 290 °C, the increase in the ionic conductivity due to improved crystallinity (to ~70%) surpasses the decrease in the ionic conductivity due to  $\text{Li}_4\text{P}_2\text{S}_6$  formation, and therefore the ionic conductivity increases to  $7.0 \times 10^{-4}$  S/cm for the SE annealed at 290 °C, but continuous increase to 320 °C leads to severe decomposition of  $\text{Li}_7\text{P}_3\text{S}_{11}$  that decreases the ionic conductivity.




## ARTICLE

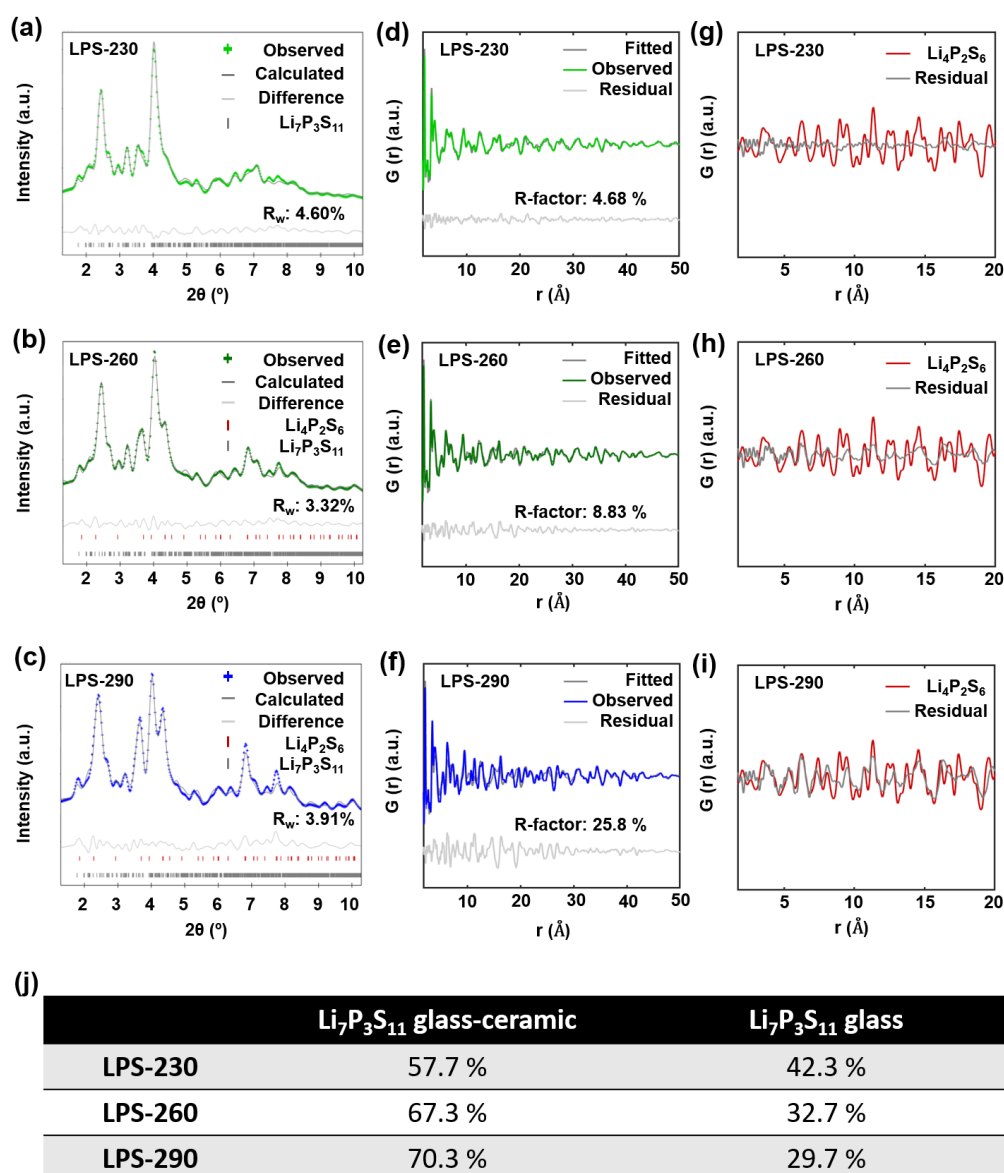

**Figure 4.** Synchrotron diffraction Bragg data of SEs annealed at 230  $^\circ\text{C}$  (a), 260  $^\circ\text{C}$  (b), and 290  $^\circ\text{C}$  (c). Reflections for LPS-230 could be assigned to crystalline  $\text{Li}_7\text{P}_3\text{S}_{11}$ , and reflections for LPS-260 and LPS-290 were refined with both  $\text{Li}_7\text{P}_3\text{S}_{11}$  and  $\text{Li}_4\text{P}_2\text{S}_6$  phases. The phase fraction of  $\text{Li}_4\text{P}_2\text{S}_6$  increases as the annealing temperature increases. Reduced PDFs of LPS-230 (d), LPS-260 (e), and LPS-290 (f) in the range of 1.7  $\text{\AA}$  and 50  $\text{\AA}$  were fitted by a linear combination of reduced PDFs of ball-milled  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass and  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass-ceramic (ball-milled glass annealed at 260  $^\circ\text{C}$  for 12 hours) to estimate the crystallinity. The R-factor is labeled on each figure. (g-i) The resulting profile differences of the linear combination fitting of SEs annealed at different temperatures were compared with the calculated reduced PDF of crystalline  $\text{Li}_4\text{P}_2\text{S}_6$ . The difference profile in (f) shows reasonably good agreement with the reduced PDF of  $\text{Li}_4\text{P}_2\text{S}_6$ . The phase fractions of  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass and  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass-ceramic in the SEs annealed at different temperatures for the linear combination fitting are included in the table (j).

## ARTICLE

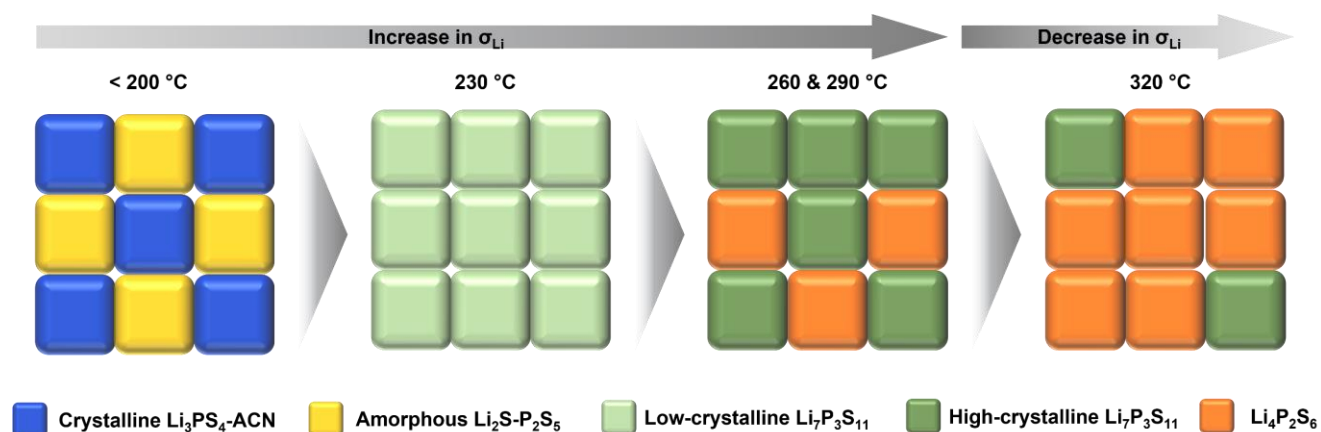

**Figure 5.** Schematic illustration of synthesis-structure-property relationship during annealing of solution-processed precursor.

### 2.5 Strategies to Increase Ionic Conductivity of Solution-Synthesized $\text{Li}_7\text{P}_3\text{S}_{11}$

The structural analysis based on synchrotron X-ray total scattering provides important insights to rationalize the structure-property relation of solution-synthesized  $\text{Li}_7\text{P}_3\text{S}_{11}$  SEs. While LPS-230 shows single-phase  $\text{Li}_7\text{P}_3\text{S}_{11}$  from lab XRD, its crystallinity is too low. Increasing the annealing temperature increases the crystallinity which is helpful for improving ionic transport and achieving the highest ionic conductivity after annealing at  $290\text{ }^\circ\text{C}$ . However, further increasing the annealing temperature to  $320\text{ }^\circ\text{C}$  will decrease the ionic conductivity because of the formation of poorly conductive  $\text{Li}_4\text{P}_2\text{S}_6$  phase due to the thermal decomposition of  $\text{Li}_7\text{P}_3\text{S}_{11}$ . Thus, a trade-off exists between improving crystallinity and suppressing decomposition. These fundamental insights also lead to effective strategies for further improving the ionic conductivity of solution-synthesized  $\text{Li}_7\text{P}_3\text{S}_{11}$  SE by overcoming this trade-off. This can be achieved by a better understanding of the nucleation and growth of  $\text{Li}_7\text{P}_3\text{S}_{11}$  during annealing. The two-step annealing process reported to facilitate crystallization of a ball-milled glass<sup>31,42</sup> could also be applied here. The thermodynamics for the glass to ceramic phase transition is also strongly dependent on the particle size. Decreasing the particle size of the solution-processed precursor, by reducing the particle size of  $\text{Li}_2\text{S}$  reactant or lowering the solvent to solids ratio, might also help to lower the crystallization temperature, although careful characterizations should also be done to study the size effect on the thermal decomposition of  $\text{Li}_7\text{P}_3\text{S}_{11}$ . Another important factor that cannot be ignored is

the existence of ACN solvent in the resulting SEs. Developing approaches that can effectively remove the solvent in the solids is also expected to increase ionic conductivity. It should also be noted that the improvement in the solvent removal process should not affect other chemical processes during the synthesis. For example, while improving the annealing time might be helpful for solvent removal, it cannot effectively improve ionic conductivity due to the enhanced decomposition of  $\text{Li}_7\text{P}_3\text{S}_{11}$  to form  $\text{Li}_4\text{P}_2\text{S}_6$  (**Figure S6**). Annealing the solution-processed precursor under vacuum is also effective to remove ACN but leads to the formation of  $\beta\text{-Li}_3\text{PS}_4$  instead of  $\text{Li}_7\text{P}_3\text{S}_{11}$  at high temperatures (**Figure S7**), possibly due to the loss of amorphous  $\text{Li}_2\text{S-P}_2\text{S}_5$  precursor under high vacuum. Additional approaches include exploring low boiling point solvent<sup>24</sup> and reducing the particle size of the solution-processed precursor to mitigate the diffusion limitation.

### 3. Conclusions

In summary, synchrotron X-ray total scattering and PDF analysis are used to study the structural evolution during annealing solution-processed precursor for the synthesis of  $\text{Li}_7\text{P}_3\text{S}_{11}$  SE at different temperatures. The solution-processed precursor consists of crystalline  $\text{Li}_3\text{PS}_4\text{-ACN}$  complex and amorphous lithium thiophosphate dried from the supernatant, and no apparent change in the structure of the precursor can be observed below  $200\text{ }^\circ\text{C}$ . The formation of  $\text{Li}_7\text{P}_3\text{S}_{11}$  was observed after annealing at  $230\text{ }^\circ\text{C}$ , but the SE formed after annealing at this temperature is confirmed to be a glass ceramic that

contains both amorphous and crystalline  $\text{Li}_7\text{P}_3\text{S}_{11}$ . Increasing the annealing temperature to 260 and 290 °C helps to improve the crystallinity of  $\text{Li}_7\text{P}_3\text{S}_{11}$ , however,  $\text{Li}_4\text{P}_2\text{S}_6$  was also formed after annealing at these temperatures due to the decomposition of  $\text{Li}_7\text{P}_3\text{S}_{11}$ . The quantitative determination of the crystallinity, based on the difference PDF method, indicates that the crystallinity of  $\text{Li}_7\text{P}_3\text{S}_{11}$  SE is lower than 70.3% after annealing at 290 °C. In addition, residual ACN is still present in the SE annealed at 290 °C, although the temperature is much higher than the boiling point of ACN. The obtained structural information helps to rationalize the synthesis-property relationship and explains why the SE annealed at 290 °C demonstrates the highest ionic conductivity based on the balance between improving the crystallinity and suppressing the decomposition. The results suggest that crystallization to a desired phase determined by lab XRD is overly simplistic to describe the success of the synthesis. Several approaches to improving crystallinity and decreasing the residual solvent while suppressing the decomposition were also discussed to develop approaches for increasing the ionic conductivity of solution-synthesized  $\text{Li}_7\text{P}_3\text{S}_{11}$ . Synchrotron X-ray total scattering combined with PDF analysis will be an important tool to identify the optimal synthetic conditions of these approaches.

## 4. Experimental

### 4.1 Materials Synthesis

The solution-processed precursor for the synthesis of  $\text{Li}_7\text{P}_3\text{S}_{11}$  SEs is prepared through the previously reported method.<sup>16</sup>  $\text{Li}_2\text{S}$  (Sigma-Aldrich, 99.98%) and  $\text{P}_2\text{S}_5$  (Sigma-Aldrich, 99%) with a molar ratio of 7:3 were mixed in the acetonitrile (ACN) solvent (Fisher Scientific, 99.8%) at 50 °C for 3 days. After removing all the solvents by drying under vacuum at 80 °C for 9 hours, the precursor was recovered and grinded before heat treatment at different temperatures from 25 to 320 °C under Argon for 1 hour. Pure  $\text{Li}_3\text{PS}_4$ -ACN crystalline complex was prepared through the same procedure but the molar ratio  $\text{Li}_2\text{S}$  and  $\text{P}_2\text{S}_5$  is 3:1.  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass and glass-ceramic synthesized by solid-state method are used as a reference sample in the work, while  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass was prepared by high-energy ball milling of the  $\text{Li}_2\text{S}$  and  $\text{P}_2\text{S}_5$  with a molar ratio of 7:3 at 510 rpm for 50 hours and the  $\text{Li}_7\text{P}_3\text{S}_{11}$  glass-ceramic was synthesized by annealing the ball-milled glass at 260 °C for 3-12 hours.

### 4.2 Materials Characterization

Lab XRD measurement is performed on a PanAnalytical X'Pert Diffractometer using a  $\text{Cu K}\alpha$  X-ray source from 15° to 70° 2 $\theta$ , at a scan rate of 1.25 min<sup>-1</sup>. Synchrotron X-ray total scattering measurements were performed at beamline 11-ID-B ( $\lambda = 0.21150$  Å), Advanced Photon Source (APS) Argonne National Laboratory. The samples were loaded in Kapton capillaries and sealed with epoxy. The neutron total scattering measurement was performed at beamline NOMAD at Spallation Neutron Source (SNS), Oak Ridge National Lab. Neutron PDF samples were loaded in the quartz tubes provided by Oak Ridge National Lab and sealed with epoxy. Raman spectroscopy is performed on a Renishaw Raman Spectrometer with a 514 nm laser beam. Scanning electron microscopy (SEM) images are taken on a Carl Zeiss Supra 55 field emission SEM.

### 4.3 Data Analysis

GSAS-II was used to calibrate and extract two-dimensional intensity vs. 2 $\theta$  histograms from the diffraction images<sup>43</sup>. We also used GSAS-II to perform Rietveld refinement of the histograms and obtain the pair distribution functions from the scattering data. A maximum scattering vector ( $Q_{\text{max}}$ ) of 30 Å<sup>-1</sup> was employed in the Fourier transform. PDFgui was used to calculate the reduced PDF of  $\text{Li}_4\text{P}_2\text{S}_6$  based on known structure models.<sup>39,44</sup> The linear combination fitting of reduced PDFs are done using Athena.<sup>45</sup> The structures were visualized using VESTA.<sup>46</sup>

### 4.4 Electrochemical Measurement

The ionic conductivities of SEs were determined from the EIS measurements (BioLogic VSP-3 Potentiostat). 150 mg SE, annealed at different temperatures, was densified at 400 MPa for 3 min in a polyether ether ketone (PEEK) housing, and two stainless steel rods were applied at each side of the SE to construct a two-blocking electrode cell. The impedance measurement was performed from 7 MHz to 10 mHz with an amplitude of 10 mV at room temperature.

## Author Contributions

We strongly encourage authors to include author contributions and recommend using [CRediT](#) for standardised contribution descriptions. Please refer to our general [author guidelines](#) for more information about authorship.

## Conflicts of interest

In accordance with our policy on [Conflicts of interest](#) please ensure that a conflicts of interest statement is included in your manuscript here. Please note that this statement is required for all submitted manuscripts. If no conflicts exist, please state that "There are no conflicts to declare".

## Acknowledgements

This work is supported by the US Department of Energy (DOE), Advanced Research Projects Agency for Energy (ARPA-E), IONICS program (Award No. DE-AR0000781). F.H. also acknowledges the support from the Priti and Mukesh Chatter Career Development Chair Professorship at the Rensselaer Polytechnic Institute. This research used resources of the Advanced Photon Source, a U.S. DOE Office of Science User Facility operated for the DOE Office of Science by Argonne National Laboratory under Contract No. DE-AC02-06CH11357. The mail-in program at Beamline 11-ID-B contributed to the data. This research used resources at the Spallation Neutron Source (SNS), a Department of Energy Office of Science User Facility operated by the Oak Ridge National Laboratory (ORNL). Neutron PDF measurement is done at the NOMAD beamline of SNS. We also thank Dr. Jue Liu at ORNL for the assistance in collecting and analyzing neutron PDF.

## References

- 1 J. Janek and W. G. Zeier, *Nat. Energy*, 2016, **1**, 1–4.
- 2 C. Sun, J. Liu, Y. Gong, D. P. Wilkinson and J. Zhang, *Nano Energy*, 2017, **33**, 363–386.
- 3 K. Tuo, C. Sun and S. Liu, *Electrochem. Energy Rev.*, 2023, **6**, 17.
- 4 F. Mizuno, A. Hayashi, K. Tadanaga and M. Tatsumisago, *Adv. Mater.*, 2005, **17**, 918–921.
- 5 N. Kamaya, K. Homma, Y. Yamakawa, M. Hirayama, R. Kanno, M. Yonemura, T. Kamiyama, Y. Kato, S. Hama, K. Kawamoto and A. Mitsui, *Nat. Mater.*, 2011, **10**, 682–686.
- 6 H.-J. Deiseroth, S.-T. Kong, H. Eckert, J. Vannahme, C. Reiner, T. Zaiß and M. Schlosser, *Angew. Chem., Int. Ed.*, 2008, **47**, 755–758.
- 7 A. Sakuda, A. Hayashi and M. Tatsumisago, *Sci. Rep.*, 2013, **3**, 1–5.
- 8 A. Banik, T. Famprikis, M. Ghidui, S. Ohno, M. A. Kraft and W. G. Zeier, *Chem. Sci.*, 2021, **12**, 6238–6263.
- 9 R. Schlem, C. F. Burmeister, P. Michalowski, S. Ohno, G. F. Dewald, A. Kwade and W. G. Zeier, *Adv. Energy Mater.*, 2021, **11**, 2101022.
- 10 A. Hayashi, S. Hama, H. Morimoto, M. Tatsumisago and T. Minami, *J. Am. Ceram. Soc.*, 2001, **84**, 477–79.
- 11 S. Boulineau, M. Courty, J.-M. Tarascon and V. Viallet, *Solid State Ion.*, 2012, **221**, 1–5.
- 12 A. Miura, N. C. Rosero-Navarro, A. Sakuda, K. Tadanaga, N. H. H. Phuc, A. Matsuda, N. Machida, A. Hayashi and M. Tatsumisago, *Nat. Rev. Chem.*, 2019, **3**, 189–198.
- 13 M. Ghidui, J. Ruhl, S. P. Culver and W. G. Zeier, *J. Mater. Chem. A*, 2019, **7**, 17735–17753.
- 14 Ö. U. Kudu, T. Famprikis, B. Fleutot, M.-D. Braidia, T. Le Mercier, M. S. Islam and C. Masquelier, *J. Power Sources*, 2018, **407**, 31–43.
- 15 Z. Liu, W. Fu, E. A. Payzant, X. Yu, Z. Wu, N. J. Dudney, J. Kiggans, K. Hong, A. J. Rondinone and C. Liang, *J. Am. Chem. Soc.*, 2013, **135**, 975–978.
- 16 Y. Wang, D. Lu, M. Bowden, P. Z. El Khoury, K. S. Han, Z. D. Deng, J. Xiao, J.-G. Zhang and J. Liu, *Chem. Mater.*, 2018, **30**, 990–997.
- 17 N. H. H. Phuc, M. Totani, K. Morikawa, H. Muto and A. Matsuda, *Solid State Ion.*, 2016, **288**, 240–243.
- 18 K. Lee, S. Kim, J. Park, S. H. Park, A. Coskun, D. S. Jung, W. Cho and J. W. Choi, *J. Electrochem. Soc.*, 2017, **164**, A2075.
- 19 T. Ates, M. Keller, J. Kulisch, T. Adermann and S. Passerini, *Energy Storage Mater.*, 2019, **17**, 204–210.
- 20 M. Calpa, N. C. Rosero-Navarro, A. Miura and K. Tadanaga, *RSC Adv.*, 2017, **7**, 46499–46504.
- 21 S. Ito, M. Nakakita, Y. Aihara, T. Uehara and N. Machida, *J. Power Sources*, 2014, **271**, 342–345.
- 22 R. C. Xu, X. H. Xia, Z. J. Yao, X. L. Wang, C. D. Gu and J. P. Tu, *Electrochim. Acta*, 2016, **219**, 235–240.
- 23 B. Fan, Q. Zhang, Z. Luo, X. Zhang, H. Ma, P. Fan and B. Xue, *Solid State Ion.*, 2019, **343**, 115073.
- 24 H. Gamo, A. Nagai and A. Matsuda, *Sci. Rep.*, 2021, **11**, 21097.
- 25 K. Yamamoto, M. Takahashi, K. Ohara, N. H. H. Phuc, S. Yang, T. Watanabe, T. Uchiyama, A. Sakuda, A. Hayashi, M. Tatsumisago, H. Muto, A. Matsuda and Y. Uchimoto, *ACS Omega*, 2020, **5**, 26287–26294.
- 26 K. Yamamoto, S. Yang, M. Takahashi, K. Ohara, T. Uchiyama, T. Watanabe, A. Sakuda, A. Hayashi, M. Tatsumisago, H. Muto, A. Matsuda and Y. Uchimoto, *ACS Appl. Energy Mater.*, 2021, **4**, 2275–2281.
- 27 M. Takahashi, S. Yang, K. Yamamoto, K. Ohara, N. H. H. Phuc, T. Watanabe, T. Uchiyama, A. Sakuda, A. Hayashi, M. Tatsumisago, H. Muto, A. Matsuda and Y. Uchimoto, *Solid State Ion.*, 2021, **361**, 115568.
- 28 J. E. Lee, K.-H. Park, J. C. Kim, T.-U. Wi, A. R. Ha, Y. B. Song, D. Y. Oh, J. Woo, S. H. Kweon, S. J. Yeom, W. Cho, K. Kim, H.-W. Lee, S. K. Kwak and Y. S. Jung, *Adv. Mater.*, 2022, **34**, 2200083.
- 29 M. Tatsumisago, S. Hama, A. Hayashi, H. Morimoto and T. Minami, *Solid State Ion.*, 2002, **154–155**, 635–640.
- 30 A. Hayashi, K. Minami and M. Tatsumisago, *J. Solid State Electrochem.*, 2010, **14**, 1761–1767.
- 31 M. R. Busche, D. A. Weber, Y. Schneider, C. Dietrich, S. Wenzel, T. Leichtweiss, D. Schröder, W. Zhang, H. Weigand, D. Walter, S. J. Sedlmaier, D. Houtarde, L. F. Nazar and J. Janek, *Chem. Mater.*, 2016, **28**, 6152–6165.
- 32 F. Marchini, B. Porcheron, G. Rousse, L. Albero Blanquer, L. Droguet, D. Foix, T. Koç, M. Deschamps and J. M. Tarascon, *Adv. Energy Mater.*, 2021, **11**, 2101111.
- 33 Y. Seino, M. Nakagawa, M. Senga, H. Higuchi, K. Takada and T. Sasaki, *J. Mater. Chem. A*, 2015, **3**, 2756–2761.
- 34 Egami, Takeshi, and Simon JL Billinge. *Underneath the Bragg peaks: structural analysis of complex materials*. Newnes, 2012.
- 35 K. W. Chapman, *MRS Bull.*, 2016, **41**, 231–240.
- 36 X. Wang, S. Tan, X.-Q. Yang and E. Hu, *Chinese Phys. B*, 2020, **29**, 028802.
- 37 K. Ohara, N. Masuda, H. Yamaguchi, A. Yao, S. Tominaka, H. Yamada, S. Hiroi, M. Takahashi, K. Yamamoto, T. Wakihara, Y. Uchimoto, F. Utsuno and S. Kimura, *Phys. Status Solidi B*, 2020, **257**, 2000106.
- 38 M. Calpa, H. Nakajima, S. Mori, Y. Goto, Y. Mizuguchi, C. Moriyoishi, Y. Kuroiwa, N. C. Rosero-Navarro, A. Miura and K. Tadanaga, *Inorg. Chem.*, 2021, **60**, 6964–6970.
- 39 C. Dietrich, M. Sadowski, S. Siculo, D. A. Weber, S. J. Sedlmaier, K. S. Weldert, S. Indris, K. Albe, J. Janek and W. G. Zeier, *Chem. Mater.*, 2016, **28**, 8764–8773.
- 40 J. Peterson, J. TenCate, T. Proffen, T. Darling, H. Nakotte and K. Page, *J. Appl. Cryst.*, 2013, **46**, 332–336.
- 41 S. Shiotani, K. Ohara, H. Tsukasaki, S. Mori and R. Kanno, *Sci. Rep.*, 2017, **7**, 6972.
- 42 K. Minami, A. Hayashi and M. Tatsumisago, *J. Am. Ceram. Soc.*, 2011, **94**, 1779–1783.
- 43 B. H. Toby and R. B. Von Dreele, *J. Appl. Cryst.*, 2013, **46**, 544–549.
- 44 C. L. Farrow, P. Juhas, J. W. Liu, D. Bryndin, E. S. Božin, J. Bloch, T. Proffen and S. J. L. Billinge, *J. Phys.: Condens. Matter*, 2007, **19**, 335219.
- 45 B. Ravel and M. Newville, *J. Synchrotron Rad.*, 2005, **12**, 537–541.
- 46 K. Momma and F. Izumi, *J. Appl. Cryst.*, 2011, **44**, 1272–1276.