

**Organic electrode materials for non-aqueous, aqueous, and all-solid-state Na-ion batteries**

Journal:	<i>Journal of Materials Chemistry A</i>
Manuscript ID	TA-REV-01-2021-000528.R1
Article Type:	Review Article
Date Submitted by the Author:	28-Feb-2021
Complete List of Authors:	Holguin, Kathryn; George Mason University, Chemistry and Biochemistry Mohammadiroudbari, Motahareh; George Mason University, Chemistry and Biochemistry Qin, Kaiqiang; George Mason University, Chemistry and Biochemistry Luo, Chao; George Mason University, Chemistry and Biochemistry

Organic electrode materials for non-aqueous, aqueous, and all-solid-state Na-ion batteries

Kathryn Holguin,^{a,1} Motahareh Mohammadiroudbari,^{a,1} Kaiqiang Qin,^a Chao Luo*^{a,b}

^aDepartment of Chemistry and Biochemistry, George Mason University, Fairfax, VA, 22030, USA

^bQuantum Science & Engineering Center, George Mason University, Fairfax, VA, 22030, USA

¹These authors contributed equally to this work

*To whom correspondence should be addressed. E-mail: cluo@gmu.edu

Abstract: Na-ion batteries (NIBs) are promising alternatives to Li-ion batteries (LIBs) due to the low cost, abundance, and high sustainability of sodium resources. However, the high performance of inorganic electrode materials in LIBs does not extend to NIBs because of the larger ion size of Na⁺ than Li⁺ and more complicated electrochemistry. Therefore, it is vital to search for high-performance electrode materials for NIBs. Organic electrode materials (OEMs) with the advantages of high structural tunability and abundant structural diversity show great promise in developing high-performance NIBs. To achieve advanced OEMs for NIBs, a fundamental understanding of the structure-performance correlation is desired for rational structure design and performance optimization. In this review, recent advances in developing OEMs for non-aqueous, aqueous, and all-solid-state NIBs are presented. The challenges, advantages, mechanisms, development, and applications of advanced OEMs in NIBs are also discussed. Perspectives for the innovation of structure design principle and future research direction of OEMs in non-aqueous, aqueous, and all-solid-state NIBs are provided.

1. Introduction

The rapid development of modern technologies, including smart devices, electric vehicles, renewable energy, and grid-scale electrical energy storage, has stimulated a substantial demand for cost-effective and sustainable energy storage devices. State-of-the-art Li-ion batteries (LIBs), consisting of graphite anodes and cobalt-rich cathodes, cannot satisfy this demand because of the high cost and limited availability of lithium resources, as well as the high cost, scarcity, and high toxicity of the cobalt resources.^{1,2} To overcome these challenges, it is pivotal to exploit advanced battery systems beyond LIBs. Among them, Na-ion batteries (NIBs) have attracted considerable research interests because of the low cost, abundance, and high sustainability of sodium resources.³⁻⁶ The fundamental chemical and physical properties of Li, Na, and K elements in various rechargeable battery systems are compared in Table 1. Though the specific/volumetric capacity of Na is lower than Li, the cost of Na is much lower than Li, and the abundance of Na in the earth's crust is three orders of magnitude higher than Li.⁷ From the overview of different types of metal anodes in rechargeable batteries (Fig. 1), Na shows advantages over Li and K in terms of cost and abundance, which makes Na resources promising for developing cost-effective and sustainable energy storage devices.⁸ In the last decade, a rich variety of inorganic electrode materials were developed for NIBs, including sodium transition metal oxides, sodium transition metal phosphates, sulfur, selenium, metal sulfides, graphite, tin, phosphorus, hard carbons, etc.⁹⁻²⁴ However, compared to lithium ion, sodium ion shows similar chemical/physical properties but a larger ion size and more complicated electrochemistry in NIBs, and thus the electrochemical performance of these inorganic electrode materials in NIBs is not comparable to that in LIBs in terms of specific capacity and cycle life.^{25,26} The development and applications of cost-effective and sustainable NIBs as next-generation energy storage devices are highly dependent on the

performance of advanced electrode materials. Developing low-cost, high-capacity, long-lifetime and high-efficiency electrode materials plays a vital role in the prospect of NIBs.

Table 1. A summary of the fundamental chemical and physical properties of metal elements in various rechargeable battery systems.

	Atomic mass	Ionic radius (Å)	E° (V) vs. SHE	Volumetric capacity (mAh mL ⁻¹)	Specific capacity (mAh g ⁻¹)	Cost (USD kg ⁻¹)	Abundance in crust (ppm)
Li	6.94	0.76	-3.04	2062	3861	19.2	20
Na	22.99	1.02	-2.713	1129	1166	3.1	23,600
K	39.1	1.38	-2.924	610	685	13.1	20,900

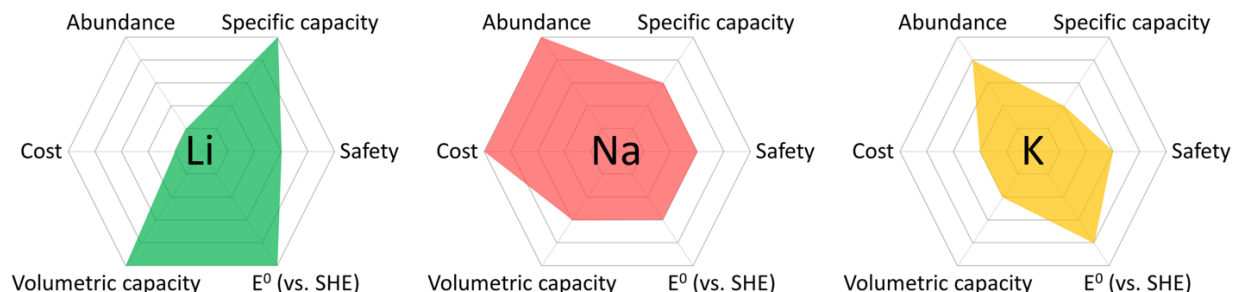


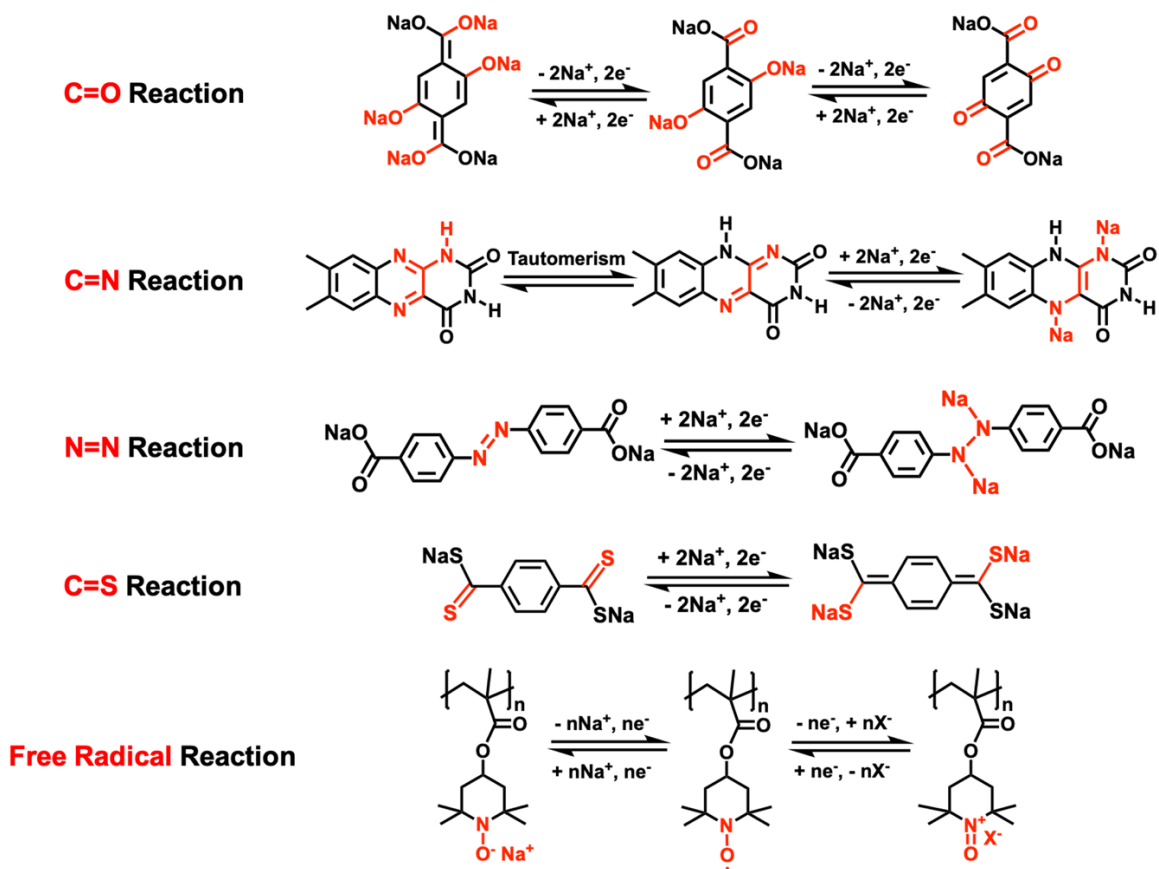
Figure 1. Overview of the fundamental properties of different types of metal anodes in rechargeable batteries.^{7,8}

The research on sodium batteries initiated in the mid-1960s, when the liquid form of sodium metal was used as a negative electrode in rechargeable batteries at high temperatures (245 °C to 350 °C).^{27,28} The low cost, lightweight, nontoxicity and abundance of sodium resources stimulated the research on high-temperature sodium-sulfur and sodium-nickel chloride (Zebra) batteries in the last century. However, the commercialization of room-temperature LIBs in the 1990s retarded the development and large-scale applications of high-temperature sodium batteries. Since then, the renaissance of sodium batteries has been dependent on the exploration of room-

temperature NIBs.^{29,30} Due to the success of advanced material synthetic techniques and nanotechnology, the research on room-temperature NIBs thrived in the last decade. Numerous sodium-based energy storage materials and nanostructures were invented to improve the capacity, cycle life, Coulombic efficiency, fast charging capability, and energy density of NIBs, whereas the performance of state-of-the-art NIBs is still not comparable with LIBs. To further promote the battery performance, developing advanced electrode materials for NIBs is pivotal.

As universal electrode materials for alkali-ion batteries, organic electrode materials (OEMs) extend their high performance in LIBs to NIBs.^{31,32} The lightweight, low cost, abundance, high sustainability, and high structural tunability of OEMs enable the rational structure design of cost-effective and sustainable energy storage organic materials for NIBs. To date, there are five types of reaction mechanisms in organic NIBs, including the carbonyl (C=O) reaction, imine (C=N) reaction, azo (N=N) reaction, thioketone/thioester (C=S) reaction, and free radical (N-O•) reaction.³³⁻³⁹ Scheme 1 summarizes these five types of reaction mechanisms by using the representative OEMs to illustrate the reversible reaction between OEMs and Na-ions/electrons in each type of reaction mechanism. The conjugated structure plays an essential role in the electrochemical properties of OEMs based on the carbonyl, imine, and thioketone/thioester reactions, enabling intramolecular electron transfer within these conjugated molecules during the reaction between functional groups and Na-ions. Therefore, when designing these OEMs, two or more carbonyl, imine, or thioketone/thioester groups are always connected by a conjugated structure such as a benzene ring to make electrochemically active organic materials. In contrast, the intramolecular electron transfer is not necessary for azo- and free radical-based OEMs, so the structural design can be more flexible. For example, a conjugated structure is not required in free radical-based OEMs.^{40,41} (2,2,6,6-Tetramethylpiperidin-1-yl)oxidanyl, commonly known as

TEMPO, is widely used in designing free radical-based OEMs. The conjugated structure is not necessary for TEMPO-based OEMs. Due to the abundant nature of organic materials, various functional groups and backbone structures can be used to manipulate their electrochemical performance in NIBs.



Scheme 1. The reaction mechanisms of various types of organic electrode materials in NIBs.³³⁻³⁹

Though OEMs show great promise in NIBs, there are still three major challenges for their development and applications: 1) low electronic conductivity, which leads to sluggish reaction kinetics; 2) high solubility in the electrolyte, which reduces the cyclic stability; 3) particle

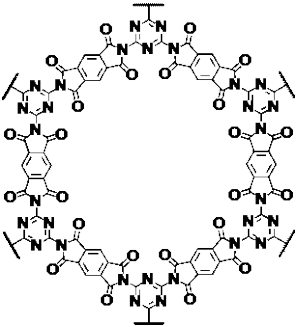


pulverization triggered by the large volume change during the sodiation/de-sodiation process, which destroys the structural integrity of organic electrodes and results in poor reaction kinetics and cyclic stability.⁴²⁻⁴⁴ To overcome these challenges, a variety of approaches have been adopted to improve the conductivity, stability, and integrity of organic electrodes. For example, a large amount (30 wt% ~ 60 wt%) of conductive carbon such as carbon black, graphene, or carbon nanotube, is used to build three-dimensional (3D) conductive networks and enhance the conductivity of the organic electrodes.⁴⁵⁻⁴⁷ Organic salt formation and polymerization of small organic compounds are two effective approaches to tuning the polarity and lipophilicity of OEMs, reducing their solubility in the liquid electrolyte.⁴⁸⁻⁵⁸ To mitigate the particle pulverization in organic electrodes, graphene oxide protection, and self-healing chemistry were used to retain the structural integrity of organic electrodes.^{43,59} Though great achievements have been obtained, the electrochemical performance of organic NIBs is still not comparable with those of commercial LIBs. The design and synthesis of novel advanced OEMs are demanded for cost-effective and sustainable NIBs. This review summarizes the recent advances in developing high-performance OEMs for non-aqueous, aqueous, and all-solid-state NIBs. The rational structure design principles and future research directions of OEMs in various types of NIBs are also discussed.

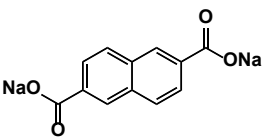





2. OEMs for non-aqueous NIBs



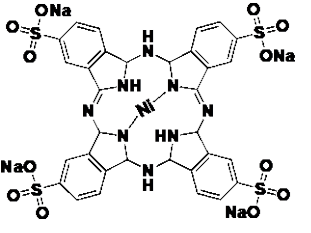

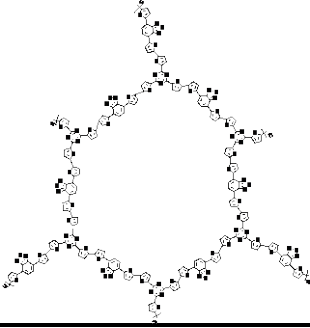
OEMs featuring low cost, lightweight, high flexibility, abundant structural diversity, and high recyclability have been extensively studied for non-aqueous NIBs.⁶⁰⁻⁶³ To fulfill the goal of cost-effective and sustainable energy storage devices, OEMs that can be derived from biomass or synthesized by natural derivatives, are promising alternatives to inorganic electrode materials in non-aqueous NIBs.⁶⁴ There are a wide range of organic compounds such as quinones, polyimides,

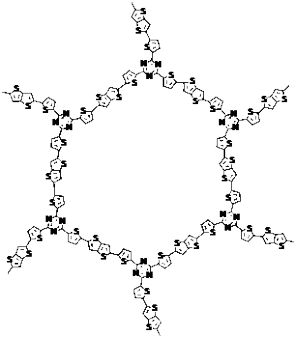





Schiff bases, azo compounds, carboxylates, etc., which have been studied as electrode materials in non-aqueous NIBs.⁶⁵⁻⁶⁷ The focus is to improve their electrochemical reaction kinetics and cycling stability by tailoring their molecular structure, mitigating particle pulverization, and reducing the solubility in the liquid electrolyte. Table 2 summarizes the chemical structure and electrochemical performance of state-of-the-art OEMs in non-aqueous NIBs.



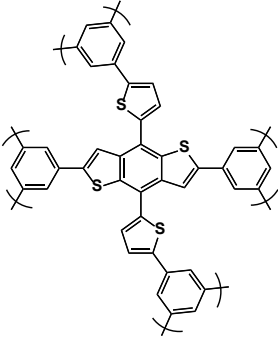

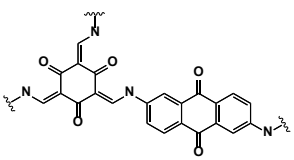
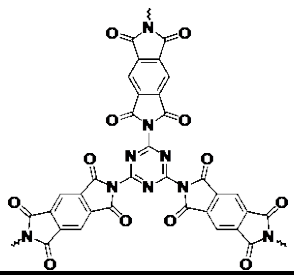
Table 2. Summary of OEMs for non-aqueous NIBs.

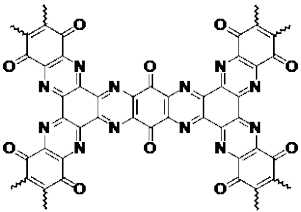




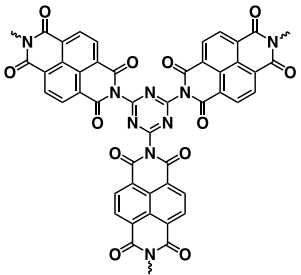
Compound	Structure	Electrolyte	Average discharge voltage	Initial reversible capacity at current density	Cycle life (n)	Rate capability
2DPI ¹²⁶		1 M NaClO ₄ in EC/DEC, 1:1 by volume	~0.2 V	312 mA h g ⁻¹ at 0.1 A g ⁻¹	1,100	137 mA h g ⁻¹ at 10 A g ⁻¹
		1M NaFSI in EC/DEC, 4:6	0.29 V	282 mA h g ⁻¹ at 0.1C	60	~150 mA h g ⁻¹ at 2C
Na ₂ C ₈ H ₄ O ₄ ^{51,52,114}		0.8 M NaClO ₄ in EC/DEC, 1:1 by volume	0.3 V	295 mA h g ⁻¹ at 30 mA g ⁻¹ (0.1C)	90	100 mA h g ⁻¹ at 10C
		1 M NaOTf diglyme	~ 0.3 V	245.2 mA h g ⁻¹ at 30 mA g ⁻¹	N/A	88.2 mA h g ⁻¹ at 1 A g ⁻¹
DHBQDS ⁵⁰		0.8 M NaClO ₄ in EC/DEC, 1:1 by volume	0.3 V	295 mA h g ⁻¹ at 30 mA g ⁻¹ (0.1C)	90	100 mA h g ⁻¹ at 10C

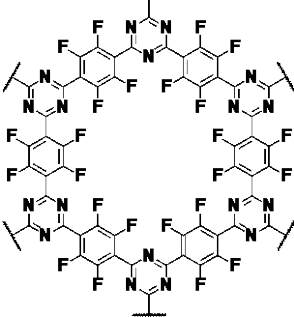


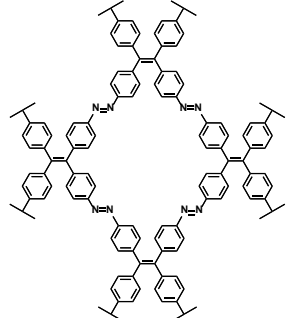

Na ₂ NDC ¹⁰⁴		1 M NaClO ₄ in PC + 3wt% FEC	~ 0.3 V	200 mA h g ⁻¹ at 0.5 C	200	133 mA h g ⁻¹ at 5 C
CHDA ¹⁴⁵		1.0 M NaClO ₄ in EC/PC, 1:1 by volume, + 5wt% FEC	~ 0.3 V	307 mA h g ⁻¹ at 0.1 A g ⁻¹	100	125 mA h g ⁻¹ at 2.0 A g ⁻¹
NaHBDC ⁵⁴		1 M NaPF ₆ EC/EMC, 3:7 by weight	~0.34 V	273 mA h g ⁻¹ at 10 mA g ⁻¹	50	N/A
SSDC ⁶⁸		1 M NaClO ₄ in PC	0.39 V	375 mA h g ⁻¹ at 50 mA g ⁻¹	400	72 mA h g ⁻¹ at 10 A g ⁻¹
Na ₃ BTC ¹⁰⁵		1 M NaBF ₄ in tetraglyme	0.42 V	558 mA h g ⁻¹ at 0.2 C	1,500	~ 210 mA h g ⁻¹ at 1 C
PTCDA ⁶⁰		1 M NaPF ₆ in EC/DMC, 1:1 by weight	~0.50 V	436.1 mA h g ⁻¹ at 25 mA g ⁻¹	300	67.7 mA h g ⁻¹ at 2 A g ⁻¹

BTAQ ¹⁰⁷		1 M NaBF ₄ in EC/DEC/DMC, 1:1:1 by volume	0.5 V	275.8 mA h g ⁻¹ at 25 mA g ⁻¹	100	105.7 mA h g ⁻¹ at 200 mA g ⁻¹
PCT ¹¹⁰		1 M NaBF ₄ in EC/DEC, 1:1 by volume, +10wt% FEC	0.5 V	133 mA h g ⁻¹ at 200 mA g ⁻¹	500	~ 40 mA h g ⁻¹ at 2 A g ⁻¹
TsNiPc@GO ¹²⁷		1 M NaPF ₆ in EC/DMC, 1:1 by volume	~ 0.5 V	600 mA h g ⁻¹ at 10 mA g ⁻¹	100	N/A
PDA ⁶¹		1 M NaPF ₆ in EC/DEC, 1:1 by weight	~0.5 V	581 mA h g ⁻¹ at 50 mA g ⁻¹	1,024	122 mA h g ⁻¹ at 3.2 A g ⁻¹
D/A-CON-10 ⁶⁷		1 M NaClO ₄ in PC/FEC, 98:2 by weight	~0.5 V	860 mA h g ⁻¹ at 100 mA g ⁻¹	150	133 mA h g ⁻¹ at 1 A g ⁻¹

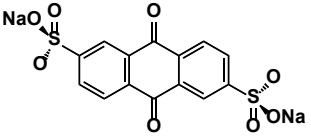





D/A-CON-16 ⁶⁷		1 M NaClO ₄ in PC/FEC, 98:2 by weight	~0.5 V	880 mA h g ⁻¹ at 100 mA g ⁻¹ 1	150	245 mA h g ⁻¹ at 1 A g ⁻¹
SCID@CNT ⁷⁷		1 M NaClO ₄ in EC/PC/FEC, 1:1:0.05 by volume	~0.5 V	231 mA h g ⁻¹ at 50 mA g ⁻¹	500	N/A
Cabpdc ¹⁰³		1 M NaClO ₄ in EC/DEC, 1:1 by volume, + 5% FEC	0.5 V	434.6 mA h g ⁻¹ at 100 mA g ⁻¹	100	150 mAh g ⁻¹ at 1 A g ⁻¹
TBC ⁶⁵		1 M NaPF ₆ in DME	0.55 V	195 mA h g ⁻¹ at 50 mA g ⁻¹	600	50 mA h g ⁻¹ at 400 mA g ⁻¹ 1
Oligomeric Schiff Bases ⁶²		1 M NaFSI in Me-THF	~0.6 V	250 mA h g ⁻¹ at C/10	50	~30 mA h g ⁻¹ at 5C
Oligomeric Schiff Bases ⁶²		1 M NaFSI in Me-THF	~0.6 V	250 mA h g ⁻¹ at C/10	50	~50 mA h g ⁻¹ at 5C





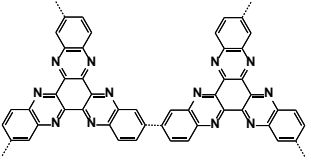
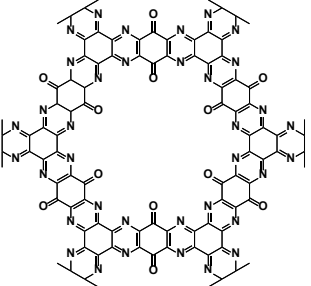
$\text{Na}_4\text{C}_{10}\text{H}_2\text{O}_8$ ¹⁴⁴		1 M NaPF_6 in EC/DEC, 1:1 by volume	0.65 V	192.7 mA h g^{-1} at 20 mA g^{-1}	1,000	78 mA h g^{-1} at 2000 mA g^{-1}
NaPTCDA ⁶⁰		1 M NaPF_6 in EC/DMC, 1:1 by weight	~0.7 V	182.3 mA h g^{-1} at 25 mA g^{-1}	120	N/A
DBD-CMP2 ¹¹⁶		1 M NaBF_4 in EC/DMC/EMC, 1:1:1 by volume	~0.75 V	414 mA h g^{-1} at 50 mA g^{-1}	100	~50 mA h g^{-1} at 2 A g^{-1}
Polymeric Schiff Base ⁵³		1 M NaFSI in Me-THF	~0.8 V	360 mA h g^{-1} at 26 mA g^{-1} (0.1C)	75	190 mA h g^{-1} at 1C
DAAQ-COF ⁷⁹		1 M NaClO_4 in EC/DMC, 1:1 by volume	~1.0 V	420 mA h g^{-1} at 100 mA g^{-1}	10,000	198 mA h g^{-1} at 5 A g^{-1}
PI-2 ¹⁴⁰		1 M NaClO_4 in EC/DEC, 1:1 by volume	~1.0 V	~280 mA h g^{-1} at 0.1 A g^{-1}	1,000	69.4 mA h g^{-1} at 5 A g^{-1}

BCP ¹⁴²		1 M NaPF ₆ in DME	~1.0 V	480.9 mA h g ⁻¹ at 1 A g ⁻¹	400	339 mA h g ⁻¹ at 10 A g ⁻¹
CADS ⁴³		1 M NaClO ₄ in EC/DMC, 1:1 by volume	~ 1.1 V	293 mA h g ⁻¹ at 20 mA g ⁻¹	100	N/A
DHBQDS ⁵⁰		1 M NaClO ₄ in FEC/DMC, 1:1 by volume	1.2 V	290 mA h g ⁻¹ at 20 mA g ⁻¹	300	68 mA h g ⁻¹ at 1 A g ⁻¹
ADASS ⁷⁶		1 M NaPF ₆ in DEGDME	1.2 V and 1.26 V	~ 220 mA h g ⁻¹ at 0.2 C	1,000	71 mA h g ⁻¹ at 40 C
Na ₂ DBQ ¹³⁹		1 M NaClO ₄ in EC/DMC, 1:1 by volume	~1.2 V	398 mA h g ⁻¹ at 0.1 C	300	160 mA h g ⁻¹ at 5 C
PI-1 ¹⁴⁰		1 M NaClO ₄ in EC/DEC, 1:1 by volume	~1.2 V	~500 mA h g ⁻¹ at 0.1 A g ⁻¹	1,000	102 mA h g ⁻¹ at 5 A g ⁻¹

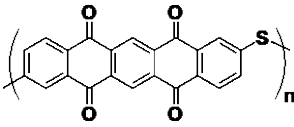


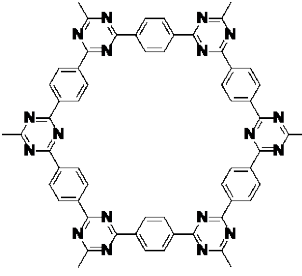



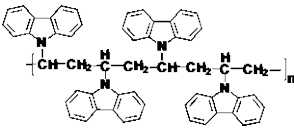

E-FCTF ¹²⁵		1 M NaClO ₄ in EC/DEC, 1:1 by volume	~ 1.2 V	332 mA h g ⁻¹ at 0.1 A g ⁻¹	200	68 mA h g ⁻¹ at 2 A g ⁻¹
Na ₂ C ₁₀ H ₂ N ₂ O ₄ ¹²⁰		0.8 M NaPF ₆ in PC	~1.2 V	~230 mA h g ⁻¹ at 1 Na/20 h	100	~10 mA h g ⁻¹ at 5C
AQ26ONa ¹⁴¹		1 M NaPF ₆ in DME	~1.2 V	245 mA h g ⁻¹ at 50 mA g ⁻¹	2,500	139 mA h g ⁻¹ at 500 mA g ⁻¹ 1
ALP-8 ¹⁰¹		1 M NaPF ₆ in DEGDME	1.2-1.5 V	315 mA h g ⁻¹ at 0.3 C	150	42 mA h g ⁻¹ at 40 C
TQA ⁶⁶		1 M NaPF ₆ in diglyme	~ 1.5 V	423.3 mA h g ⁻¹ at 100 mA g ⁻¹	100	N/A


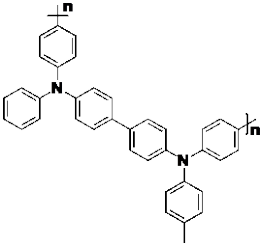

TSAQ ⁶⁹		1 M NaClO ₄ in EC/DMC, 1:1 by weight	~ 1.5 V	395 mA h g ⁻¹ at 50 mA g ⁻¹	2,500	220 mA h g ⁻¹ at 1000 mA g ⁻¹
Na ₂ PDHBQS/ RGO ¹²¹		1 M NaClO ₄ in TGM	~1.5 V	179 mA h g ⁻¹ at 100 mA g ⁻¹	150	147 mA h g ⁻¹ at 1 A g ⁻¹
DAPT-TFP-CPF ¹²⁴		1 M NaPF ₆ in DME	~1.6 V	257.5 mA h g ⁻¹ at 1 A g ⁻¹	1,400	100 mA h g ⁻¹ at 5,000 mA g ⁻¹
PAQS ¹⁰⁹		1 M NaTFSI in DOL/DME, 1:1 by volume	1.3 V and 1.76 V	134 mA h g ⁻¹ at 100 mA g ⁻¹	200	~ 120 mA h g ⁻¹ at 1 A g ⁻¹
AQDS ¹⁰²		1 M NaClO ₄ in EC/DEC, 1:1 by volume	1.73V and 1.62 V	195 mA h g ⁻¹ at 30 mA g ⁻¹	100	114 mA h g ⁻¹ at 480 mA g ⁻¹
DHAQNa ¹¹¹		1 M NaClO ₄ in EC/DMC, 1:1 by volume	~ 1.75 V	176 mA h g ⁻¹ at 0.1 C	100	~ 40 mA h g ⁻¹ at 2 C

Na ₂ AQ26DS ¹³²		1 M NaPF ₆ in DME	~1.75 V	137 mA h g ⁻¹ at 50 mA g ⁻¹	1,200	N/A
ALX ⁴⁷		1 M NaPF ₆ in DEGDME	~1.8 V	255 mA h g ⁻¹ at 50 mA g ⁻¹	N/A	N/A
LC ⁴⁷		1 M NaPF ₆ in DEGDME	~1.8 V	~222 mA h g ⁻¹ at 50 mA g ⁻¹ 1	N/A	N/A
Na ₄ DHTPA ⁷⁸		1 M NaClO ₄ in EC/DMC, 1:1 by volume	1.8 V	223 mA h g ⁻¹ at 19 mA g ⁻¹ (C/10)	100	~190 mA h g ⁻¹ at 37.4 mA g ⁻¹ (0.2 C)
UP ¹¹³		1 M NaBF ₄ in DME	1.8 V	148.3 mA h g ⁻¹ at 100 mA g ⁻¹	1,000	91.8 mA h g ⁻¹ at 3 A g ⁻¹
OAP ¹¹³		1 M NaBF ₄ in DME	1.8 V	137.8 mA h g ⁻¹ at 100 mA g ⁻¹	1,000	107.8 mA h g ⁻¹ at 3 A g ⁻¹

PDI-UI ¹⁰⁸		1 M NaClO ₄ in EC/DEC, 1:1 molar ratio	1.9 V	119 mA h g ⁻¹ at 25 mA g ⁻¹	50	~112 mA h g ⁻¹ at 200 mA g ⁻¹
Na ₂ C ₆ O ₆ ^{59,70}		1 M NaClO ₄ in FEC/EC/DMC , 2:3:5 by volume	~2.0 V	205 mA h g ⁻¹ at 20 mA g ⁻¹	500	~102 mA h g ⁻¹ at 1 A g ⁻¹
Na ₂ C ₆ O ₆ ^{59,70}		0.6 M NaPF ₆ in DEGDME	~2.0 V	484 mA h g ⁻¹ at 50 mA g ⁻¹	50	371 mA h g ⁻¹ at 1 A g ⁻¹
Ni-TTO ⁶³		1 M NaPF ₆ in DME	~2.0 V	155 mA h g ⁻¹ at 0.1 A g ⁻¹	100	118 mA h g ⁻¹ at 5 A g ⁻¹
PHATN ⁷¹		4 M NaPF ₆ in DME	2.12 V	251 mA h g ⁻¹ at 50 mA g ⁻¹	50,000	105 mA h g ⁻¹ at 25 C
TQBQ-COF ⁷²		1 M NaPF ₆ in DEGDME	2.2 V	452 mA h g ⁻¹ at 20 mA g ⁻¹	1,000	134.3 mA h g ⁻¹ at 10 A g ⁻¹

PTCDA ^{60,73}		1 M NaClO ₄ in PC	~2.2 V	~135 mA h g ⁻¹ at 100 mA g ⁻¹	500	76 mA h g ⁻¹ at 71 C
PT ⁷⁵		0.3 M Na[TFSI]/ILs	~2.2 V	301 mA h g ⁻¹ at 20 mA g ⁻¹	100	~180 mA h g ⁻¹ at 300 mA g ⁻¹
NTCDA ¹¹⁵		1 M NaClO ₄ in EC/DMC/EM C, 1:1:1 by volume, + 2% FEC	2.2 V	157 mA h g ⁻¹ at 100 mA g ⁻¹ ₁	500	112 mA h g ⁻¹ at 1 A g ⁻¹
PI ¹⁴³		1 M NaPF ₆ in EC/DMC, 1:1 by volume	~2.2 V	207 mA h g ⁻¹ at 200 mA g ⁻¹ ₁	100	39 mA h g ⁻¹ at 500 mA g ⁻¹ ₁
PTCDA ¹³⁸		1 M NaPF ₆ in EC/DEC, 1:1 by volume	~2.2 V	140 mA h g ⁻¹ at 10 mA g ⁻¹	300	91 mA h g ⁻¹ at 1,000 mA g ⁻¹
PI ²¹³⁷		1 M NaPF ₆ in EC/DMC, 1:1 by weight	~2.2 V	148.9 mA h g ⁻¹ at 0.1 C	5,000	50 mA h g ⁻¹ at 40 C
TAPQ ¹²³		4 M NaTFSI in TEGDME	~2.2 V	~250 mA h g ⁻¹ at 0.5C	NA	NA
PYT-TABQ/rGO ¹²⁹		1 M NaPF ₆ in DME	~2.2 V	~210 mA h g ⁻¹ at 1 A g ⁻¹	1,400	141.5 mA h g ⁻¹ at 8 A g ⁻¹

PPTS ¹²²		1 M NaPF ₆ in DME	1.2-2.4 V	290 mA h g ⁻¹ at 1 A g ⁻¹	2,000	155 mA h g ⁻¹ at 10 A g ⁻¹
P5Q ⁷⁴		1 M NaClO ₄ in EC/DMC/FEC	2.5 V	418 mA h g ⁻¹ at 0.1 C	300	201 mA h g ⁻¹ at 1 C
C4Q ⁷⁵		0.3 M Na[TFSI]/ILs	~ 2.5 V	406 mA h g ⁻¹ at 20 mA g ⁻¹	300	343 mA h g ⁻¹ at 45 mA g ⁻¹
BPOE ⁵⁶		1 M NaClO ₄ in PC	~2.5 V	~200 mA h g ⁻¹ at 10 mA g ⁻¹	7,000	~40 mA h g ⁻¹ at 5 A g ⁻¹
Q-TTF-Q ¹³⁰		2.5 M NaTFSI in PC	2.6 V	232 mA h g ⁻¹ at 40 mA g ⁻¹	10	N/A
PP-PS ¹³⁵		1 M NaPF ₆ in EC/DEC, 1:1 by volume	~3.15 V	75 mA h g ⁻¹ at 40 mA g ⁻¹	350	N/A
PDPPD ¹²⁸		0.5 M NaPF ₆ in EC/PC, 1:1 by volume	3.38V	94 mA h g ⁻¹ at 1C	1,000	~35 mA h g ⁻¹ at 100C
PVK-3 ¹³¹		1 M NaPF ₆ in EC/DEC, 1:1 by volume	3.4 V	110 mA h g ⁻¹ at 50 mA g ⁻¹	900	33 mA h g ⁻¹ at 500 mA g ⁻¹
Ppy/DS ¹³³		1 M NaPF ₆ in EC/DEC, 1:1 by volume	~3.5 V	115 mA h g ⁻¹ at 50 mA g ⁻¹	70	85 mA h g ⁻¹ at 50 mA g ⁻¹

OPr ¹³⁶		1 M NaClO ₄ in PC	~3.5 V	121 mA h g ⁻¹ at 20 mA g ⁻¹	50	10 mA h g ⁻¹ at 500 mA g ⁻¹
PTPAn ¹³⁴		DOL/DME, 1:1 by volume, Saturated with NaPF ₆	~3.6 V	98 mA h g ⁻¹ at 50 mA g ⁻¹	200	88 mA h g ⁻¹ at 20 C
DCBQ ¹⁰⁶		1 M NaBF ₄ in PC	N/A	175.8 mA h g ⁻¹ at 10 mA g ⁻¹	1,000	82.1 mA h g ⁻¹ at 200 mA g ⁻¹

Note: *The electrochemical performances of the OEMs are collected from the full-cell data, because the half-cell data were not reported.

2.1 Molecular structure design

The extension of π conjugated structures is a feasible strategy to improve the electrochemical reaction kinetics and achieve the fast-charging capability of OEMs in non-aqueous NIBs. The conjugated structure is able to stabilize the charged/discharged states while facilitating ion diffusion. Wang *et al.* synthesized (sodium 4,4-stilbene-dicarboxylate) SSDC through a one-pot eco-friendly reaction (Fig. 2a), offering an extended π -conjugation linkage between two carboxylate groups.⁶⁸ The SSDC anodes were tested in half cells with the sodium metal as a counter electrode at high current densities to evaluate the capacity and cycle life. The SSDC anode delivered a specific capacity of 247 mA h g⁻¹ at 1 A g⁻¹ in the first cycle with an initial Coulombic efficiency of 80% (Fig. 2b). The Coulombic efficiency was enhanced to 98% after 5 cycles while the capacity stabilized at 160 mA h g⁻¹. After 400 cycles, a reversible capacity of 112 mA h g⁻¹ was retained with capacity retention higher than 70%, demonstrating exceptional cycle life at a high current density. Moreover, the SSDC anode delivered reversible capacities of 105 mA h g⁻¹ at 2 A g⁻¹ and 72 mA h g⁻¹ at 10 A g⁻¹, demonstrating fast-charging capability in non-aqueous NIBs. This superior high-rate performance is attributed to the extended π -conjugation structure, which not only improves the charge transport and stabilizes the charged/discharged states but also enhances the intermolecular interaction and the resulting terrace packing structure.

Another strategy to improve the electrochemical performance of OEMs in non-aqueous NIBs is stabilizing α -C intermediate radicals by the resonance and steric effects. The highly reactive α -C radicals are formed in OEMs during the sodiation/de-sodiation process, triggering undesired side reactions and thus reducing the electrochemical performance. To design a stabilized α -C radical intermediate, Wu *et al.* fabricated highly stable tri-carbonyl-based anodes by diminishing the reactivity of radical intermediates.⁶⁹ Tris *N*-salicylideneanthramine, TSAA, and

tris *N*-salicylideneanthraquinoylamine, TSAQ, were synthesized by a facile metallic catalyst-free condensation reaction (Fig. 2c). The carbonyl group (C=O) in TSAA and TSAQ could undergo the electron reduction, leading to the breakage of the tri- β -ketoenamine system and the formation of a benzyl radical (α -C radical) intermediate. Subsequently, the resonance effect of the aromatic ring structures together with the steric hindrance of the large-size substitution groups in TSAA and TSAQ was able to stabilize the benzyl radical intermediate. The reversible specific capacities of 172 mA h g⁻¹ and 366 mA h g⁻¹ were achieved for TSAA and TSAQ at 50 mA g⁻¹, respectively, suggesting \sim 5.5 and \sim 11.5 Na⁺ per molecule could participate in the electrochemical redox reactions. More importantly, TSAQ delivered a high-rate performance of 220 mA h g⁻¹ at 1000 mA g⁻¹ (Fig. 2d) and showed no obvious capacity degradation after 2,500 cycles (Fig. 2e), demonstrating excellent rate capability and cycle life. This work provided a structure design strategy to stabilize the α -C radical intermediate formed in organic anodes during the sodiation/desodiation process, which may also be beneficial for the structure design of other organic energy storage systems.

In addition to these organic anodes, the structure design for organic cathodes in non-aqueous NIBs is also significant. Lee *et al.* studied the four-sodium ion storage mechanism of disodium rhodizonate (Na₂C₆O₆) as one of the best candidates for cathodes in NIBs.⁷⁰ The redox mechanism of disodium rhodizonate is demonstrated in figure 2f. The α -phase of Na₂C₆O₆ transfers into γ -phase due to the thermodynamic preference. The removal of sodium ions during the charge mitigates the reverse structural change, leading to permanent desodiation. As a result, the charged electrode remains as partially sodiated intermediate (Na_{2+x}C₆O₆) in γ -phase. The research suggested the redox capability can be significantly improved by reducing the particle size and selecting a good electrolyte. The selected electrolyte, diethylene glycol dimethyl ether

(DEGDME), could diminish the cation-anion interactions and result in the most efficient phase transformation. The four-electron process in the Na-ion cell was evaluated at a large potential window of 0.5 V – 3.2 V. The nanoparticle electrode (Nano/DEGDME) revealed a reversible capacity of 498 mA h g⁻¹ at 50 mA g⁻¹, which is about 95% of the theoretical capacity as shown in figure 2g. Even with an increased mass loading of up to 20 mg cm⁻², Na₂C₆O₆ still retained a reversible capacity of 428 mA h g⁻¹ along with an areal capacity of 8.56 A h cm⁻² (Fig. 2h), demonstrating great promise for practical applications. The complete utilization of organic cathodes at high mass loading offers opportunities for developing cost-effective and sustainable organic NIBs.

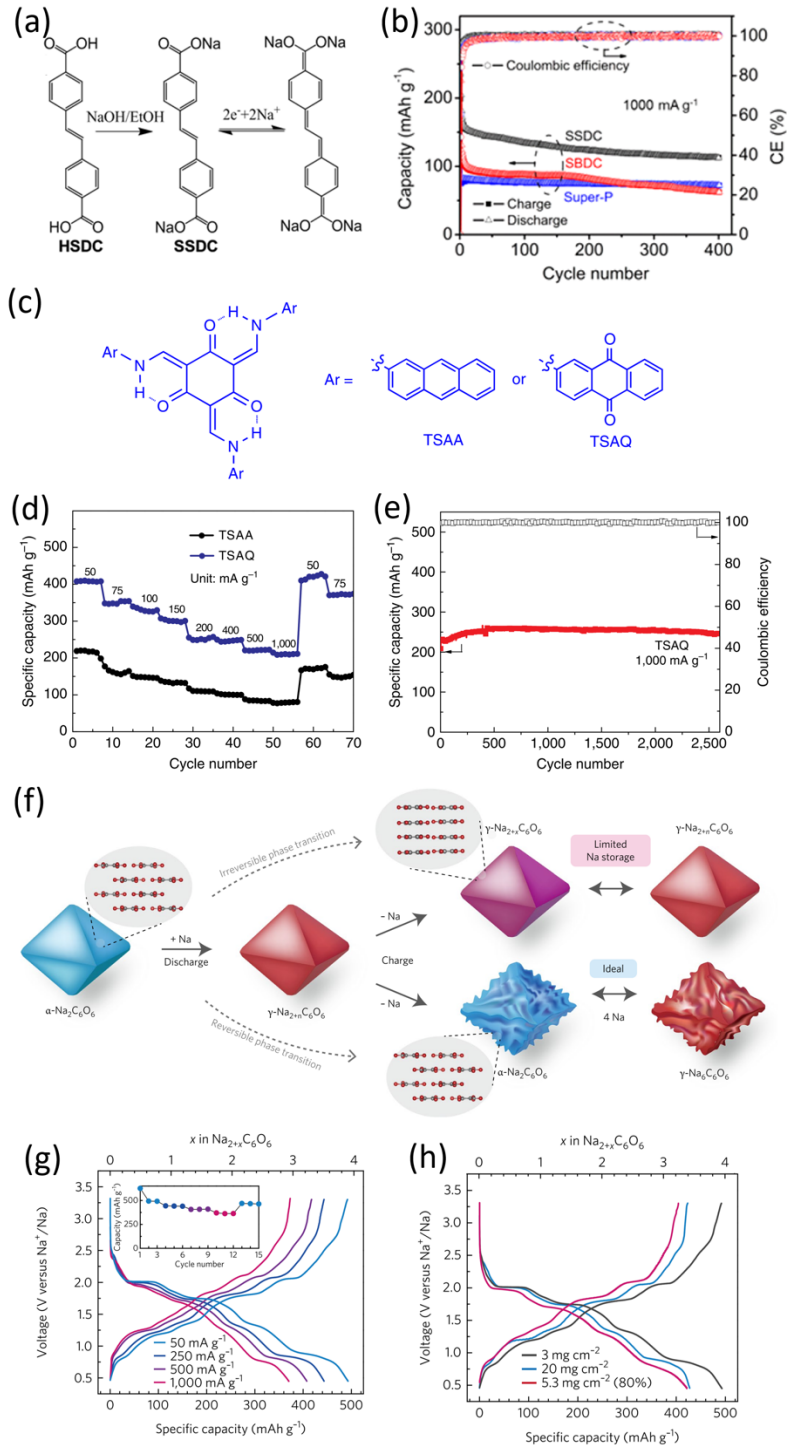


Figure 2. (a) Schematic diagram for the synthesis and reversible Na-ion insertion/extraction mechanism of SSDC. (b) Cyclability of SSDC (black, the rate capability of Super-P (blue) and SBDC (red) are also presented for comparison) under a current density of 1 A g^{-1} . Reproduced

with permission.⁶⁸ Copyright 2015 American Chemical Society. (c) Design of β -ketoenamine-linked compound-based organic electrode. Chemical structure of TSAA and TSAQ. (d) Rate performance of TSAA and TSAQ electrodes at various current densities. (e) Cycle performance and the corresponding Coulombic efficiency of TSAQ at a current density of $1,000 \text{ mA g}^{-1}$ in the voltage range of 3–0.05 V for more than 2,500 cycles. Reproduced with permission.⁶⁹ Copyright 2016 Springer Nature. (f) A schematic of the proposed de/sodiation mechanism of $\text{Na}_2\text{C}_6\text{O}_6$. During charging, the structural change from the α - to the γ -phase is kinetically suppressed. This leads to a premature desodiation, which results in limited sodium storage in subsequent cycles. Nevertheless, the reversible phase transformation becomes possible by decreasing the particle size and selecting a proper electrolyte, which in turn facilitates ideal four-sodium storage in $\text{Na}_2\text{C}_6\text{O}_6$. (g) Rate capability and corresponding cycle performance (inset) of $\text{Na}_2\text{C}_6\text{O}_6$ electrodes from 0.5–3.3 V. (h) Voltage profiles of $\text{Na}_2\text{C}_6\text{O}_6$ electrodes with high active content (80% $\text{Na}_2\text{C}_6\text{O}_6$, 5.3 mg cm^{-2}) and high mass loading (60% $\text{Na}_2\text{C}_6\text{O}_6$, 20 mg cm^{-2}) compared with the original condition (60% $\text{Na}_2\text{C}_6\text{O}_6$, 3 mg cm^{-2}). Reproduced with permission.⁷⁰ Copyright 2017 Macmillan Publishers Limited.

The polymeric structure design for OEMs can also affect the electrochemical performance in non-aqueous NIBs. Mao *et al.* suggested hexaazatrinaphthalene (HATN), which contains imine functional groups with a high theoretical capacity of 418 mA h g^{-1} , to be used as a cathode for non-aqueous NIBs.⁷¹ By polymerizing this organic compound, the more stable PHATN was obtained which was not only used in NIBs but also in multivalent (Mg and Al) rechargeable batteries. The simulated geometry and insertion potential versus Na/Na^+ for $\text{Na}_m(\text{HATN})_n$ was calculated by density functional theory (DFT), and the discharge voltage profile was found in different ratios

(Fig. 3a). The rate capability and cycle life of PHATN in 4M NaPF₆/dimethoxyethane (DME) electrolyte were tested in NIBs with sodium metal as the counter electrode. As shown in figure 3b, a small capacity decrease from 220 mA h g⁻¹ to 164 mA h g⁻¹ was observed with elevated current density from C/8 to 5C. Even at high current densities of 12C and 25C, PHATN still retained the reversible capacities of 138 mA h g⁻¹ and 105 mA h g⁻¹, respectively, and an ultra-long cycle life of 50,000 cycles was achieved at 25C with 83.8% capacity retention (Fig. 3c), indicating the fast reaction kinetics and stable cyclic stability. The excellent electrochemical performance of PHATN makes it a promising cathode for rechargeable batteries. In addition to PHATN, covalent organic frameworks (COFs) with porous structures while containing active groups such as C=O and C=N offer redox sites for sodium-ion storage. The size of pores is very important, and it should be adjusted based on the size of sodium ions to make the ion transport facile and efficient. The synthesis of triquinoxalinylene and benzoquinone (TQBQ) by using a triple condensation reaction between tetraminophenone and cyclohexanone yielded a new COF skeleton to be used in NIBs.⁷² The carbonyl groups provide multiple redox sites to store up to 12 Na⁺, while pyrazine groups link the building blocks in TQBQ-COF two-dimensional structures (Fig. 3d). The reaction mechanism was exploited by characterizing the corresponding absorption peaks for the active groups (C=O/C=N) during charge and discharge using *in-situ* Fourier-transform infrared spectroscopy (FTIR, Fig. 3e), confirming that carbonyl groups and imine groups are redox-active centers to reversibly react with Na-ions and electrons. The TQBQ-COF-based electrode delivered a high capacity of 452.0 mA h g⁻¹ at 0.02 A g⁻¹ (Fig. 3f) and high cycling stability of ~96% capacity retention after 1,000 cycles at a high current density of 1.0 A g⁻¹ (Fig. 3g). The honeycomb-like morphology of the insoluble TQBQ-COF combined with doped nitrogen improved the electronic

conductivity and ion/electron transport. The porous architecture of nitrogen-rich COFs promises high-power NIBs.

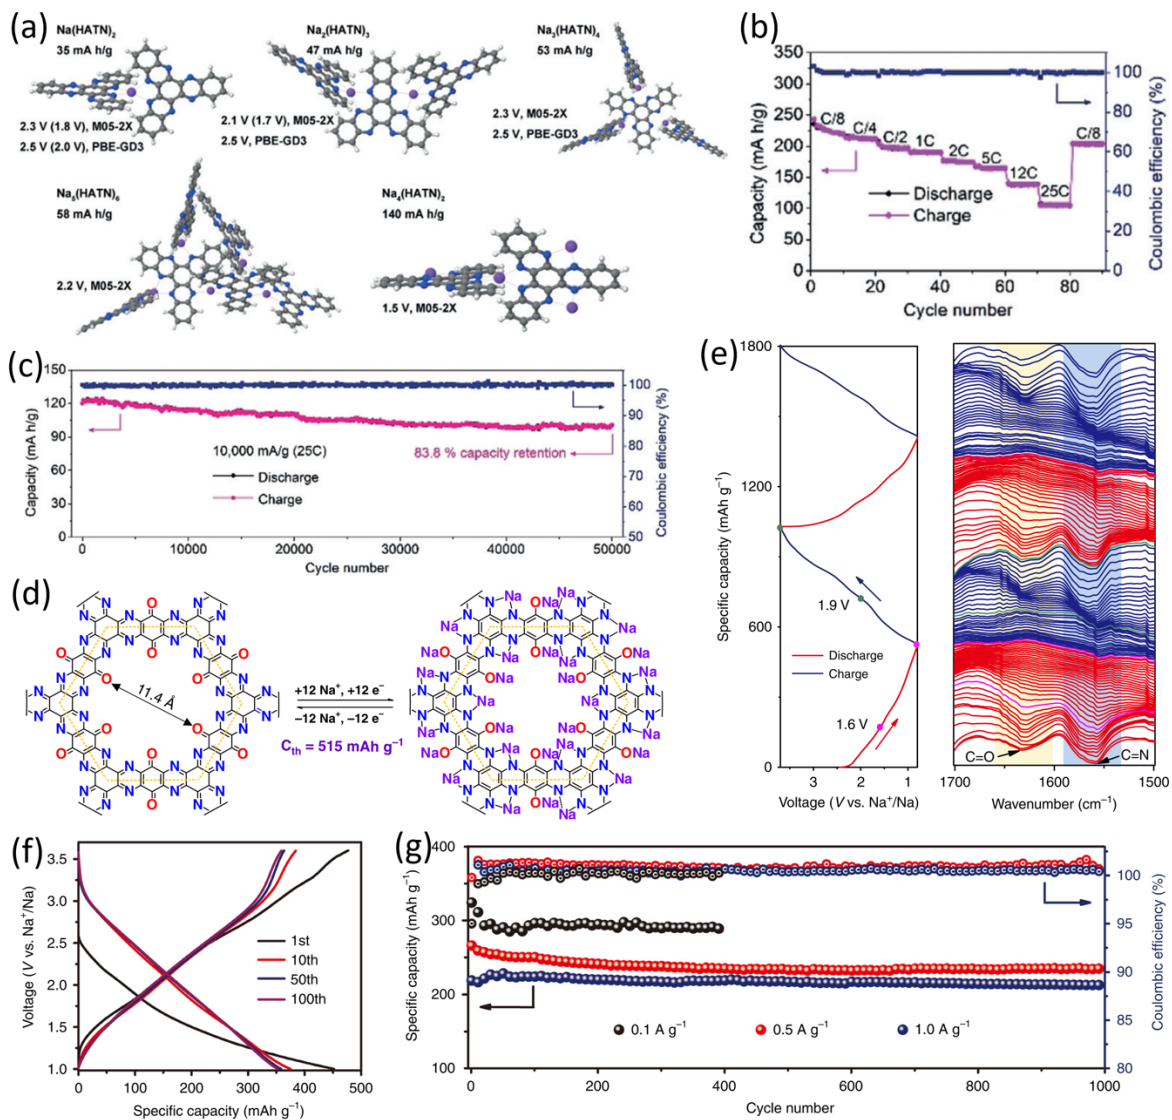


Figure 3. (a) Optimized geometries and insertion potentials vs. Na/Na⁺ of the Na_m(HATN)_n complexes surrounded by implicit solvent from DFT calculations using M05-2X/6–31+G(d,p) and PBE-GD3/6–31+G(d,p) DFT calculations. (b) Rate capability at various current densities from C/8 to 25 C. (c) Long-term cycling performance of PHATN under the current densities of 10 A g⁻¹ (25C) for 50,000 cycles. Reproduced with permission.⁷¹ Copyright 2019 Wiley-VCH Verlag

GmbH & Co. KGaA. (d) The chemical structure and possible electrochemical redox mechanism of TQBQ-COF with a theoretical capacity of 515 mA h g⁻¹. (e) *In-situ* FTIR spectra collected at different states. (f) Charge–discharge profiles of the TQBQ-COF electrode at 0.02 A g⁻¹. (g) Long cycling stability of TQBQ-COF electrodes at different current densities (0.1, 0.5, and 1.0 A g⁻¹). The capacities are all calculated based on the mass of TQBQ-COF. Reproduced with permission.⁷² Copyright 2020 Springer Nature.

2.2 Particle pulverization mitigation

The large volume change during cycling is another existing challenge for high-energy NIBs. Luo *et al.* developed two approaches to overcome this challenge: 1) wrapping OEMs with graphene oxide to accommodate the volume change and mitigate particle pulverization;⁴³ 2) employing self-healing chemistry to suppress the resulting mechanical fracture by establishing connections between the polymer binder and active material.⁵⁹ In the first approach, graphene oxide wrapped croconic acid disodium salt (CADS) was designed and synthesized.⁴³ The particle pulverization of CADS was alleviated by graphene oxide, resulting in an improved reversible capacity and cycle life. In the second approach, sodium rhodizonate dibasic (SRD) was used as a model to study the self-healing chemistry between the active material and the polymer binder in non-aqueous NIBs.⁵⁹ Although SRD contains the highest number of oxygen atoms among organic electrodes (Fig. 4a), it undergoes pulverization caused by large volume expansion. The two of carbonyl groups in fully sodiated SRD could form hydrogen bonds with hydroxyl-rich binders. Sodium alginate (SA) as a hydroxyl-rich binder and polyvinylidene fluoride (PVDF) as a hydroxyl-free binder were chosen to demonstrate the self-healing chemistry between the electrode material and the binder (Fig. 4b). FTIR spectra confirmed the formation of hydrogen bonds, which

results in the deformation of pyranose rings in the SA binder. This was confirmed by the disappearance of the FTIR peak at $\sim 1300\text{ cm}^{-1}$ for the SRD-SA film. To investigate the role of the binder, the electrochemical performance of SRD with the SA binder and the PVDF binder was compared. As shown in figure 4c and 4d, SRD-SA electrodes showed much better cycle life of 500 cycles and higher rate capability up to 1 A g^{-1} in non-aqueous NIBs due to the self-healing chemistry between SRD and the SA binder. This work opened a new door for the application of self-healing chemistry in rechargeable batteries.

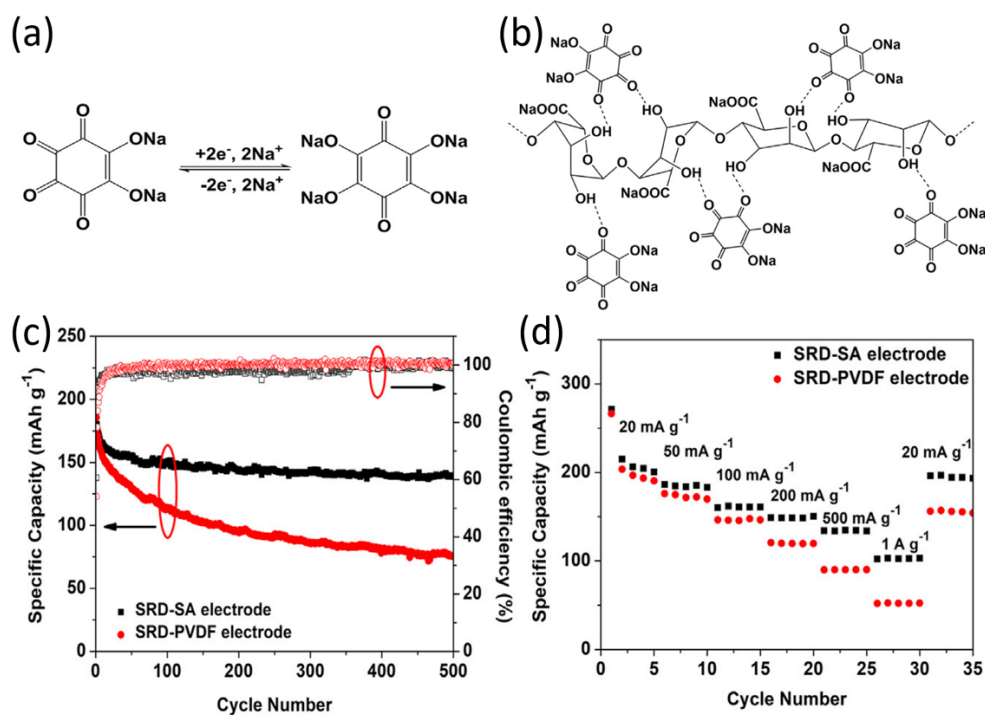


Figure 4. (a) The sodiation-desodiation mechanism for SRD. (b) Schematic illustration of hydrogen bonding between SRD and SA. (c) Cycle life of the SRD-PVDF and SRD-SA electrodes at a current density of 50 mA g^{-1} . (d) Rate capability of the SRD-SA and SRD-PVDF electrodes. Reproduced with permission.⁵⁹ Copyright 2017 Elsevier Inc.

2.3 Dissolution inhibition

Due to the high solubility of OEMs in the liquid electrolyte, their dissolution induces fast active material loss and capacity decline in non-aqueous NIBs. Several strategies such as surface coating, carbon encapsulation, electrolyte optimization, organic salt formation, and polymerization have been used to mitigate the dissolution of OEMs. Recently, surface modification at the atomic level was introduced as an effective strategy to stabilize organic electrodes. Zhao *et al.* and Luo *et al.* used a gas-phase atomic layer deposition (ALD) technique to deposit a thin layer (2~5 nm) of Al₂O₃ on the surface of disodium terephthalate and 2,5-Dihydroxy-1,4-benzoquinone disodium salt electrodes to improve their cyclic stability in non-aqueous NIBs.⁵⁰ The Al₂O₃ coating acts as an artificial solid electrolyte interphase (SEI) layer to protect the organic electrode from dissolution into the liquid electrolyte and enhance the electrochemical performance. Thangavel *et al.* also applied ultrathin metal oxide coatings on the surface of perylene-3,4,9,10-tetracarboxylic acid dianhydride (PTCD) via the ALD technique.⁷³ Two of the carbonyl groups in PTCD act as active centers to reversibly react with Na-ions and electrons (Fig. 5a). The metal oxide coatings (Al₂O₃, ZnO, and TiO₂) can form a stable interphase to protect the PTCD electrodes from dissolution and improve the electrochemical kinetics and cyclic stability of PTCD electrodes. All the coated electrodes showed better cycle life and higher rate capability than the pristine electrodes, because the PTCD dissolution in the organic electrolyte was mitigated by the coating layer (Fig. 5b and 5c). The PTCD electrode coated with TiO₂ (Ti-PTCD) exhibited better electrochemical performance than the other two coatings (Al₂O₃ and ZnO) in terms of rate capability and cycle life. The Ti-PTCD electrode showed a stable cycle life and low polarization for 500 cycles. These results demonstrated that surface modification is an effective method to enhance the interphase stability and cycle life of organic electrodes.

Quinone-based organic electrodes have been widely studied in non-aqueous NIBs due to their low cost, abundance, and high sustainability. However, the quinone derivatives also suffer from high solubility in the liquid electrolyte. To circumvent this challenge, the composite structure of Pillar[5] quinone (P5Q) was built by encapsulating P5Q in ordered mesoporous carbon (CMK-3) and single-walled carbon nanotubes (SWCNT).⁷⁴ Xiong *et al.* further introduced poly(ethylene glycol) (PEG) as a gel polymer electrolyte to restrain the solubility of P5Q. The discharge-charge mechanism of the P5Q cathode is illustrated in figure 5d, indicating that carbonyl groups play an important role in the redox reaction with Na-ions and electrons. The large surface area of CMK-3 allows better diffusion and absorption of sodium ions while SWCNTs are beneficial in creating a 3D conductive network around the P5Q. The initial capacity of 418 mA h g⁻¹ at 0.1 C was achieved for the P5Q/CMK-3/SWCNT cathode, and a reversible capacity of 290 mA h g⁻¹ was retained after 300 cycles (Fig. 5e), demonstrating superior cycling stability. Furthermore, P5Q/CMK-3 with a ratio of 1:2 delivered higher rate capability and better cycle life than pure P5Q and P5Q/CMK-3 with a ratio of 1:1 in non-aqueous NIBs, suggesting that a higher content of CMK-3 could reduce capacity decay and stabilize the cathode. The P5Q/CMK-3 composites represent a promising structure for stabilizing organic cathodes in non-aqueous NIBs.

The effort to improve the stability of quinone-based cathodes has not been limited to structure optimization. Selecting the best electrolyte with adjustable physicochemical properties such as weaker polarity and lower donor numbers is another method to enhance the performance of organic cathodes.⁷⁵ Among various organic electrolytes, ionic liquids (ILs) have been exploited in non-aqueous NIBs based on organic quinone cathodes. In general, ILs were composed of cations such as *N*-methyl-*N*-propylpyrrolidinium [PY13], *N*-butyl-*N*-methylpyrrolidinium [PY14], and *N*-methyl-*N*-propyl piperidinium [PP13], and anions such as bis(fluorosulfonyl)imide [FSI] and

bis(trifluoromethanesulfonyl)imide [TFSI] (Fig. 5f). Wang *et al.* evaluated the performance of five types of *para*-quinone small molecules including 1,4-benzoquinone (*p*-BQ), 4,4'-dimethyl-1,1'-bi(cyclohexa-3,6-diene)-2,2',5,5'-tetraone (DBT), 9,10-anthraquinone (AQ), 5,7,12,14-pentacenetetrone (PT), Calix[4]quinone (C4Q) in non-aqueous NIBs. The inhibitory effect of different ILs toward the dissolution of quinone electrode materials is shown in figure 5g. Weaker polarity, lower donor number of ILs, and small interaction energy between the active material and ILs suppress the dissolution of OEMs in the electrolyte. The interaction energy between quinone cathodes and ILs was calculated using DFT. According to the results, [PY13][TFSI] - *p*-BQ and [PY14][FSI] - *p*-BQ showed the smallest and largest interaction energy, respectively. Therefore, [PY13][TFSI], in which *p*-BQ has the lowest solubility, was selected for the electrochemical test. As shown in figure 5h, the [PY13][TFSI] based electrolyte in the Na/C4Q cell exhibited a much better cycle life (300 cycles) than the DME-based electrolyte, demonstrating that developing ILs-based electrolytes is a promising method to address the dissolution challenge of OEMs in non-aqueous NIBs.

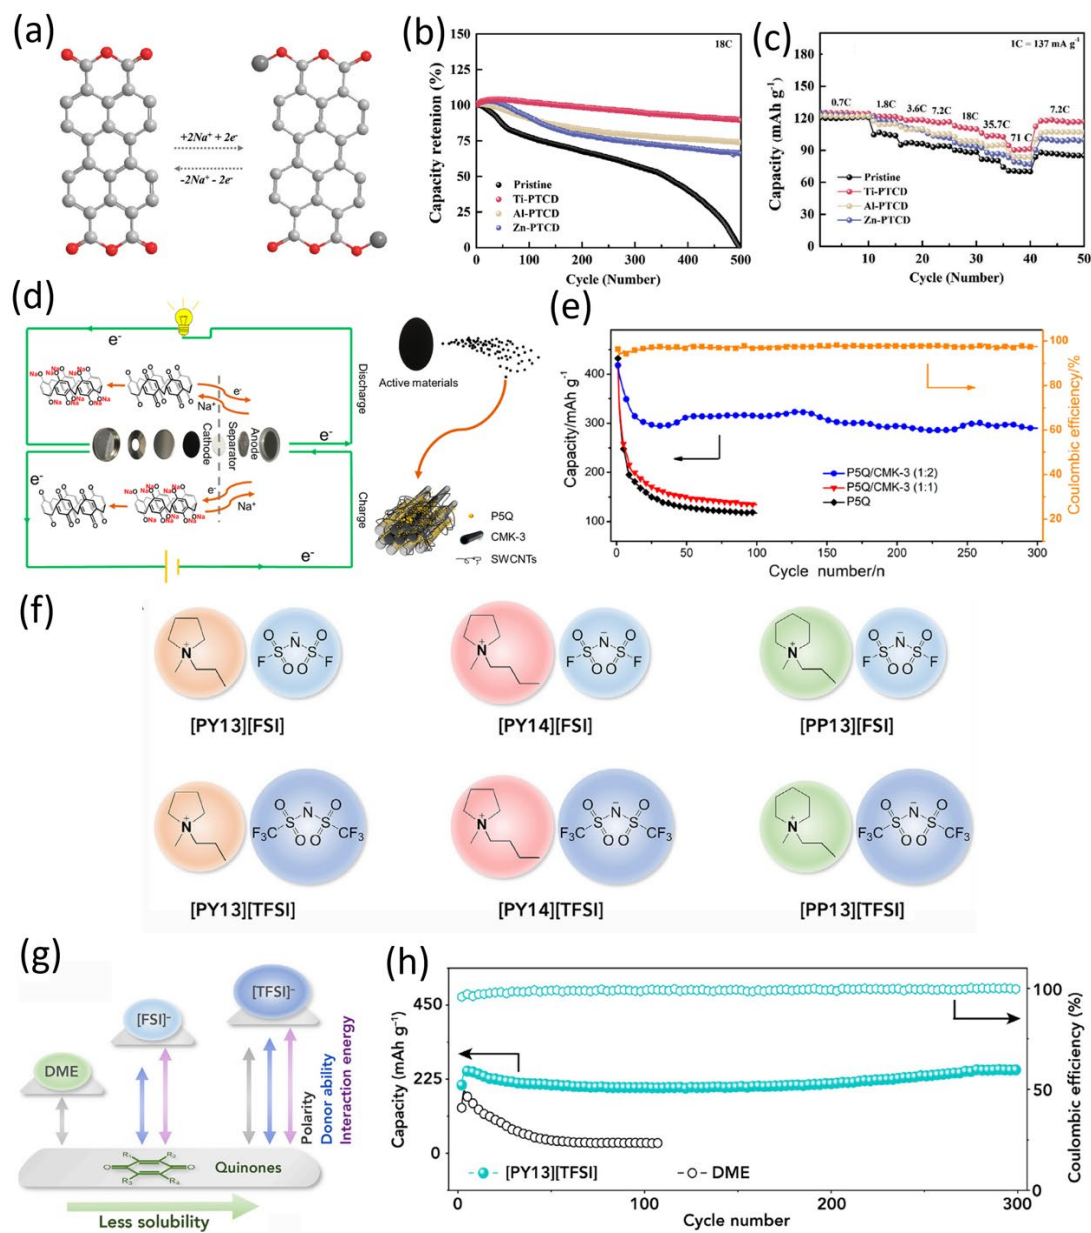


Figure 5. (a) Sodium-ion storage mechanism in a PTCD organic molecule. (b) Cyclic stability for different metal oxide-coated (2 cycles) PTCD samples at 18C (2.5 A g⁻¹). (c) Rate performance of PTCD, and metal oxide-coated PTCD (2 cycles). Reproduced with permission.⁷³ Copyright 2020 Wiley-VCH GmbH. (d) Schematic of the discharge-charge of P5Q cathode and sodium-metal anode. During the discharge, electrons in sodium metal lose and pass through the separator to reach P5Q. At the same time, the carbonyl groups gain electrons and sodium ions are embedded in the

carbonyl groups of P5Q. The charging process is the opposite way. (e) Discharge capacities of P5Q and P5Q/CMK-3 at 0.1 C and Coulombic efficiency of P5Q/CMK-3 (1:2). Reproduced with permission.⁷⁴ Copyright 2019 American Chemical Society. (f) Chemical structures of six ionic liquids in this study. (g) Schematic comparison of polarity, donor ability, and quinone-solvent interactive energy for DME and ionic liquids. (h) Cycling stability of C4Q cathode at 130 mA g⁻¹ (0.29 C) in 0.3 M Na[TFSI]/DME and 0.3 M Na[TFSI]/[PY13][TFSI] electrolyte. The cathode consists of 50 wt % C4Q, 40 wt % conducting carbon, and 10 wt % binder. Reproduced with permission.⁷⁵ Copyright 2018 Elsevier Inc.

In addition to surface coating, carbon encapsulation, and electrolyte optimization, organic salt formation and polymerization of small organic molecules are also effective strategies to overcome the dissolution challenge of OEMs in the electrolytes. A novel azo group based organic anode was designed by Luo *et al.*⁷⁶ The azo compounds with and without carboxylate groups in figure 6a showed different electrochemical behaviors in non-aqueous NIBs because of the dissolution of azo compounds. Azobenzene (AB) without a carboxylate group is highly soluble in the electrolyte and suffers from very fast capacity fading, while 4-(phenylazo)benzoic acid sodium salt (PBASS) with one carboxylate group attached to azobenzene shows improved cyclic stability. Azobenzene-4,4'-dicarboxylic acid sodium salt (ADASS) with two carboxylate groups exhibited the best electrochemical performance (Fig. 6b and 6c) in terms of fast charging capability (up to 40C) and long cycle life (2,000 cycles). The carboxylated azo compounds represent a new family of organic anodes for high-performance NIBs. Another example of organic salts in non-aqueous NIBs is sodium 5,5'-carbonylbis(isobenzofuran-1,3-dione) (SCID) synthesized from two sodium phthalate bridged by carbonyl groups.⁷⁷ The structure and mechanism of Na ion

insertion/extraction in SCID is illustrated in figure 6d. The bridging carbonyl group is able to activate the adjacent carbonyl groups in SCID, accommodating four sodium ions and leading to a high initial capacity of 231 mA h g^{-1} at 50 mA g^{-1} . At a higher current density of 100 mA g^{-1} , an initial capacity of 155 mA h g^{-1} is achieved, and a reversible capacity of 83 mA h g^{-1} can still be retained after 500 cycles (Fig. 6e). This work confirmed that organic salt formation is an effective strategy to overcome the high solubility challenge of OEMs in non-aqueous NIBs.

To use OEMs as both the cathode and anode in all-organic batteries for high-sustainability energy storage devices, Wang *et al.* developed a unique organic salt, organic tetrasodium salt of 2,5-dihydroxyterephthalic acid ($\text{Na}_4\text{C}_8\text{H}_2\text{O}_6$) with enolate and carboxylate groups.⁷⁸ The redox couples of $\text{Na}_2\text{C}_8\text{H}_2\text{O}_6/\text{Na}_4\text{C}_8\text{H}_2\text{O}_6$ at 2.3 V in the positive electrode and $\text{Na}_4\text{C}_8\text{H}_2\text{O}_6/\text{Na}_6\text{C}_8\text{H}_2\text{O}_6$ at 0.3 V in the negative electrode were employed in the all-organic NIBs. The reaction mechanism is shown in figure 6f, indicating the alkoxide groups act as active centers in the positive electrode and carboxylate groups act as active centers in the negative electrode. The conjugated benzene ring, combined with both types of functional groups, stabilizes the redox intermediates in the electrochemical process. The excellent performance of $\text{Na}_4\text{C}_8\text{H}_2\text{O}_6$ in the symmetric full cell was confirmed by various electrochemical tests. In the cutoff window from 0.2 V to 2.6 V, the full cell delivered high charge and discharge capacities of 223 mA h g^{-1} and 198 mA h g^{-1} with an average discharge voltage of $\sim 1.8 \text{ V}$ (Fig. 6g). In addition, the full cell was stably tested for 100 cycles with the Coulombic efficiency close to 99% (Fig. 6h), demonstrating great promise for high-sustainability NIBs. Therefore, organic salt formation is an effective strategy to overcome the high solubility challenge of OEMs and achieve high-performance organic cathodes and anodes for non-aqueous NIBs.

As is well known, the solubility of organic compounds decreases as their molecular weight increases. Hence, redox-active polymers are widely used in non-aqueous NIBs to solve the high solubility challenge. As previously discussed, COFs with crystalline structures and π -conjugated skeletons can offer high electrochemical performance in non-aqueous NIBs. To gain fundamental understanding of electrochemical behaviors of COFs, facile synthesis of β -Ketoenamine linked DAAQ-COF from 1,3,5-triformylphloroglucinol was used to prepare the two dimensional (2D)-COFs with different thicknesses (Fig. 6i).⁷⁹ The effect of thickness on the electrochemical performance of COFs was investigated at different conditions. The results demonstrated a lower thickness is more favorable in improving the capacity and cyclic stability. The high capacity of 420 mA h g⁻¹, excellent rate capability of 198 mA h g⁻¹ at a high current density of 5 A g⁻¹, and outstanding cycling stability (10,000 cycles) for the DAAQ-COF with a thickness of 4-12 nm confirm that the thin 2D-COFs are promising for non-aqueous NIBs. Further studies can be done to design an exfoliated structure of COFs, where the thickness remains low enough for high-rate electrochemical reactions in non-aqueous NIBs. Therefore, based on the knowledge gained from the recent progress of OEMs in non-aqueous NIBs, more research efforts could be devoted to the rational design of molecular structures, organic electrolytes, interphase layers, hybrid composites, and polymeric frameworks to further optimize the electrochemical performance of OEMs in non-aqueous NIBs.

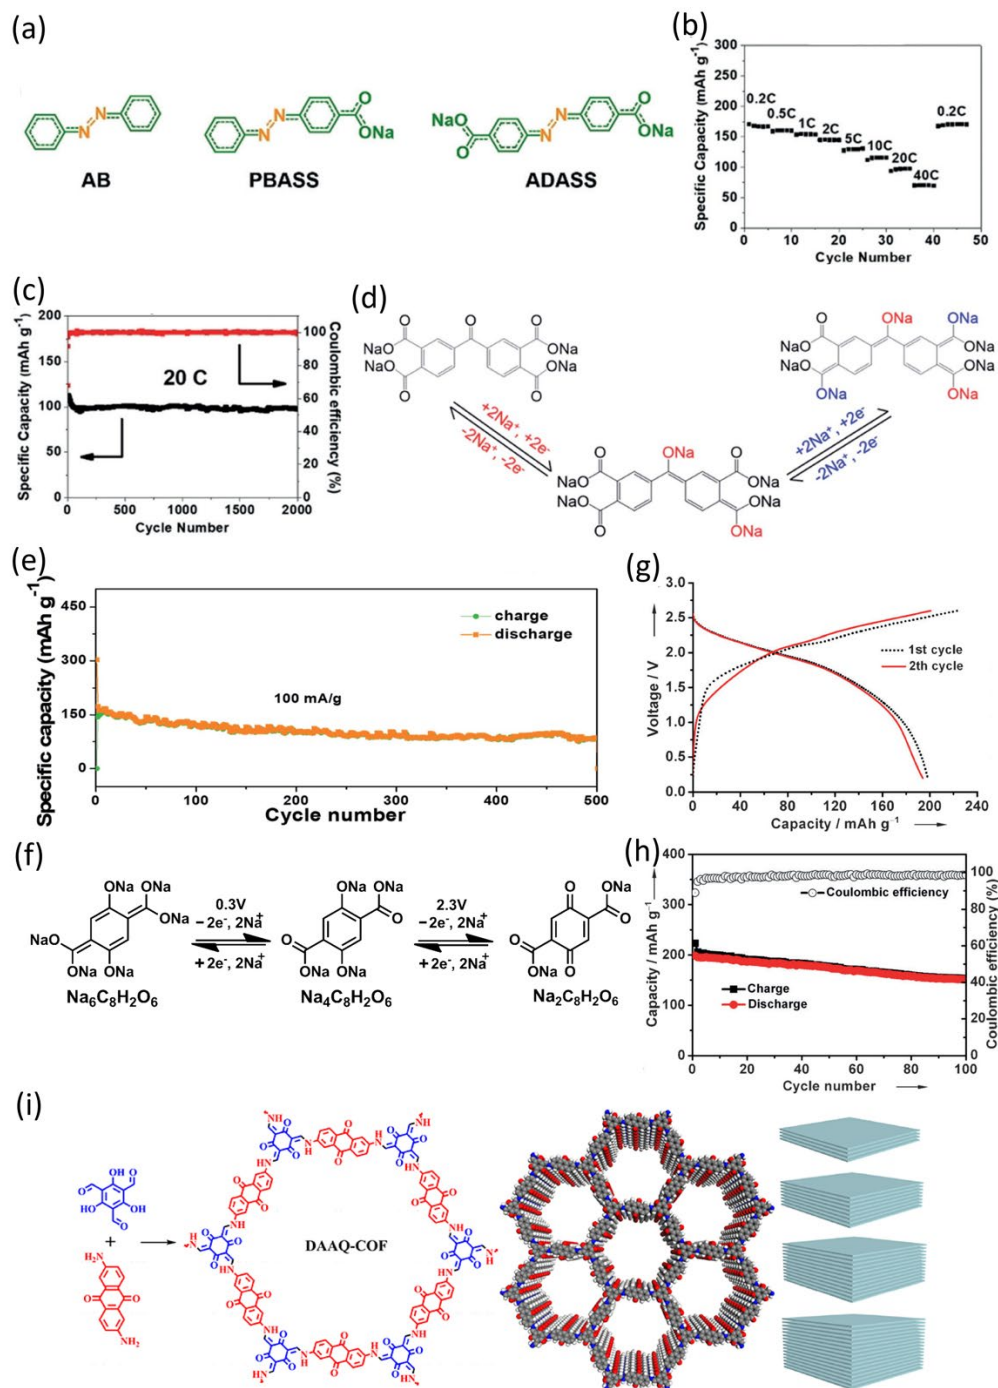



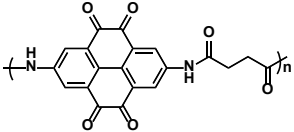



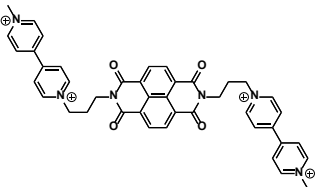
Figure 6. (a) Molecular structure of AB, PBASS, and ADASS. (b) Rate performance at various C-rates. (c) De-sodiation capacity and Coulombic efficiency versus cycle number at 20C. Reproduced with permission.⁷⁶ Copyright 2018 Wiley-VCH Verlag GmbH & Co. KGaA. (d) The proposed mechanism of Na ion insertion/extraction into/from the molecular structure of SCID.






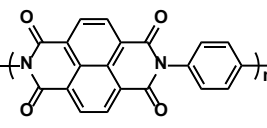
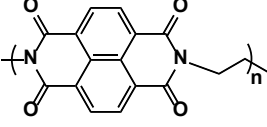

Electrochemical performance of SCID/Na half cells in the voltage range of 0.01–3.0 V. (e) Cycling performance of SCID@CNT at current densities of 100 mA g⁻¹. Reproduced with permission.⁷⁷ Copyright 2020 The Royal Society of Chemistry. (f) Electrochemical redox reaction mechanism of Na⁺ ions with Na₄C₈H₂O₆/Na₆C₈H₂O₆ and Na₂C₈H₂O₆/Na₄C₈H₂O₆ at potentials of 0.3 V and 2.3 V, respectively. (g) Galvanostatic charge/discharge voltage profiles of the full cells assembled with Na₄DHTPA under a current density of 19 mA g⁻¹. (h) Cycling and Coulombic efficiency under a current density of 19 mA g⁻¹. Reproduced with permission.⁷⁸ Copyright 2014 Wiley-VCH Verlag GmbH & Co. KGaA. (i) Synthetic route and simulated structures of DAAQ-COF and illustration of the Layer-by-Layer Stacking in 2D-COF with different thickness. Reproduced with permission.⁷⁹ Copyright 2019 American Chemical Society.



3. OEMs in aqueous NIBs

Aqueous NIBs are promising alternatives to LIBs due to their high affordability, sustainability, and environmental benignity. However, their performance was limited by the narrow electrochemical stability window of aqueous electrolytes due to electrochemical water splitting at high and low potentials.⁸⁰ Many high-performance electrode materials such as graphite, silicon, sodium metal, hard carbons, and sodium transition metal oxides do not show good performance in aqueous NIBs. It is of great significance to develop high-performance electrode materials for aqueous NIBs. Here, the tunable molecular structure and adjustable redox potentials make OEMs promising electrode materials for aqueous NIBs.⁸¹⁻⁸³ A number of high-performance OEMs compatible with aqueous battery systems have been explored and are presented in this section, including carbonyl compounds and imine compounds. Table 3 summarizes the chemical structure and electrochemical performance of state-of-the-art OEMs in aqueous NIBs.

Table 3. Summary of OEMs for aqueous NIBs.

Compound	Structure	Electrolyte	Average discharge voltage	Initial reversible capacity at current density	Cycle life (n)	Rate capability
PTCDI ^{112*}		1 M Na ₂ SO ₄ aqueous electrolyte	-0.5 V vs Ag/AgCl	357 F g ⁻¹ at 200 mA g ⁻¹	1,000	103 F g ⁻¹ at 9 A g ⁻¹
PPTO ^{86*}		5 M NaNO ₃ in H ₂ O	~0 V	201 mA h g ⁻¹ at 1C	80	N/A
NatMel-Na ¹¹⁸		1 M Na ₂ SO ₄ in H ₂ O	~0.1 V vs MSE	30.4±1.6 mA h g ⁻¹ at 10 mA g ⁻¹	30	N/A
SynMel-Na ¹¹⁸		1 M Na ₂ SO ₄ in H ₂ O	~0.15 V vs MSE	31.1±2.0 mA h g ⁻¹ at 10 mA g ⁻¹	30	N/A
E-SynMel-Na ¹¹⁸		1 M Na ₂ SO ₄ in H ₂ O	~0.2 V vs MSE	24.1±2.0 mA h g ⁻¹ at 10 mA g ⁻¹	30	N/A
MNV ^{94*}		2.5 M NaClO ₄ in H ₂ O	~0.4 V	63 mA h g ⁻¹ at 0.3 A g ⁻¹	700	~50 mA h g ⁻¹ at 2.4 A g ⁻¹

PNTCDA ^{91*}		1 M Na ₂ SO ₄ in H ₂ O	~0.5 V	134.4 mA h g ⁻¹ at 10C	1,000	112 mA h g ⁻¹ at 1.8 A g ⁻¹
Polyimide ^{90*}		5 M NaNO ₃ in H ₂ O	~0.6 V	184 mA h g ⁻¹ at 500C	20	N/A
4-HT-Benzene ^{88*}		8 M NaClO ₄ in H ₂ O	~0.6 V vs SCE	52 mA h g ⁻¹ at 0.075 A g ⁻¹	100	~62 mA h g ⁻¹ at C/10
PTAm ¹¹⁹		0.1 M NaBF ₄ in H ₂ O	0.66 V vs Ag/AgCl	114 mA h g ⁻¹ at 60 C	1,000	N/A
PNZ ^{93*}		10 M NaOH in H ₂ O	~0.7 V	277 mA h g ⁻¹ at 0.5 A g ⁻¹	1,500	92 mA h g ⁻¹ at 30 A g ⁻¹
PNP ^{89*}		1 M Na ₂ SO ₄ in H ₂ O at pH 7	~0.8 V	132.2 mA h g ⁻¹ at 10C	500	92 mA h g ⁻¹ at 20C
PNTCDA ^{92*}		1 M NaNO ₃ in H ₂ O	~0.8 V	95 mA h g ⁻¹ at 20 A g ⁻¹	50,000	28 mA h g ⁻¹ at 100 A g ⁻¹
ALO ^{95*}		1 M CF ₃ SO ₃ Na in H ₂ O	1 V	149 mA h g ⁻¹ at 0.2 A g ⁻¹	100	146 mA h g ⁻¹ at 10C

Alizarin ^{87*}		Gel Electrolyte (2.2 g PVA, 1.4 g NaClO ₄ in 10 mL H ₂ O)	~1 V	233.1 mA h g ⁻¹ at 5 A g ⁻¹	N/A	115.8 mA h g ⁻¹ at 15 A g ⁻¹
SNDI ^{84*}		1 M Na ₂ SO ₄ in H ₂ O at pH 7	~1.1 V	76 mA h g ⁻¹ at 500 mA g ⁻¹	500	N/A

Note: *The electrochemical performances of the OEMs are collected from the full-cell data, because the half-cell data were not reported.

Carbonyl compounds are widely used in rechargeable batteries due to their low cost, abundance, and flexible structural tunability. The redox potentials for some carbonyl compounds such as quinone derivatives and imides are in the range of 1.5 V to 3.0 V versus Na/Na⁺, which is within the stability window of the electrolyte in aqueous NIBs. Kim *et al.* developed disodium naphthalene diimide (SNDI) as an anode for aqueous NIBs (Fig. 7a).^{84,85} SNDI is partially protonated and becomes (H)-SNDI when exposed to the aqueous electrolyte. The (H)-SNDI delivered sodiation and desodiation peaks at -0.25 V and -0.03 V versus standard hydrogen electrode (SHE), respectively, and when evaluated in a half cell at 6 C (516 mA g⁻¹), the organic anode delivered a reversible capacity of 62 mA h g⁻¹ (Fig. 7b). These reduction/oxidation peaks and capacity indicate that 0.7 Na⁺ ions reversibly bind with SNDI. A hybrid aqueous sodium-ion full cell based on the (H)-SNDI anode and a Prussian blue analogue (KCo_{0.5}Cu_{0.5}Fe(CN)₆) cathode, demonstrated an average potential of ~1.1 V, and a specific capacity of 34 mA h g⁻¹ at a high rate of 20 C (1,720 mA g⁻¹) during charging and 10 C (860 mA g⁻¹) during discharging (Fig. 7c). The full cell exhibited a stable cycle life of 100 cycles with 88% capacity retention, demonstrating great promise in aqueous NIBs.

Quinone derivatives, which are widely used as electrode materials in non-aqueous NIBs, have also been used in aqueous NIBs. These compounds undergo an ion-coordination mechanism whereby, during reduction, cations (Na^+) bind to the reduced carbonyl group (C-O^-) and then during oxidation, cations (Na^+) are dissociated with the restored carbonyl group (Fig. 7d).⁸⁶ Recently, Liang *et al.* developed multiple aqueous battery systems (H^+ , Li^+ , Na^+ , K^+ , and Mg^{2+}), utilizing quinone-based monomers and polymers. A quinone-based monomer, pyrene-4,5,9,10-tetraone (PTO), was initially investigated as an anode material, however, it was found to be soluble in aqueous electrolytes.⁸⁶ To address this challenge, PTO was polymerized to generate polymerized pyrene-4,5,9,10-tetraone (PPTO), which was proved to be insoluble in aqueous electrolytes. The PPTO anode delivered a high specific capacity of 201 mA h g^{-1} with 79% capacity retention over 80 cycles, when paired with a $\text{Na}_3\text{V}_2(\text{PO}_4)_3$ cathode in a neutral 5M NaNO_3 aqueous electrolyte (Fig. 7e). Long *et al.* investigated another quinone derivative, Alizarin, as an organic anode in aqueous NIBs.⁸⁷ Alizarin nanowires were obtained through an antisolvent self-assembly method (Fig. 7f). The nanowire electrode delivered a high specific capacity of $233.1 \text{ mA h g}^{-1}$ at a current density of 5 A g^{-1} , representing one of the best anodes in aqueous NIBs. When paired with polypyrrole (Fig. 7g), a biodegradable and highly compatible cathode material, the full cell demonstrated an average discharge potential of $\sim 1.06 \text{ V}$ and an initial specific capacity of $151.8 \text{ mA h g}^{-1}$ at a current density of 1 A g^{-1} . The cell retained a discharge capacity of 62.8 mA h g^{-1} even at a high current density of 5 A g^{-1} (Fig. 7h). All these results confirm that carbonyl compounds are promising for developing aqueous NIBs.

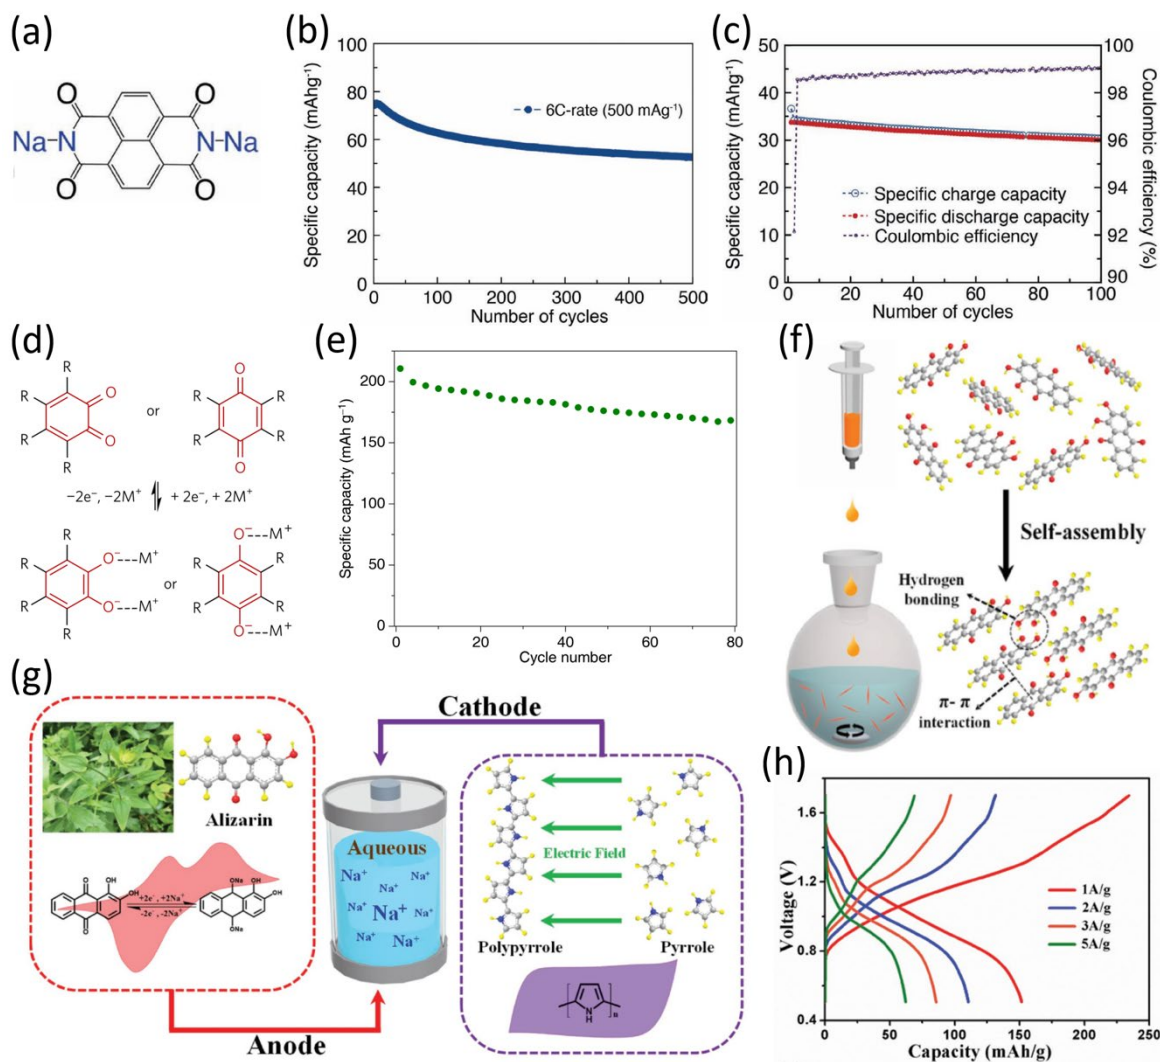


Figure 7. (a) Structure of (H)SNDI. (b) Discharging cycling performance of (H)SNDI measured at 6C. The C-rates were the same for charge and discharge in each cycle. $1C = 86 \text{ mA g}^{-1}$. (c) The cycling performance and Coulombic efficiency of the given full cell. Reproduced with permission.⁸⁴ Copyright 2014 WILEY-VCH Verlag GmbH & Co. KGaA. (d) Reaction mechanism for common quinones, (e) Cycling performance of PPTO- $\text{Na}_3\text{V}_2(\text{PO}_4)_3$ full cell (5 M NaNO_3 at 1 C). Reproduced with permission.⁸⁶ Copyright 2017 Macmillan Publishers Limited. (f) Preparation of alizarin nanowires via antisolvent self-assembly. (g) Schematic and mechanism of Alizarin-polypyrrole full cell. (h) Galvanostatic curves of the full cell with alizarin nanowires and

polypyrrole at different current densities. Reproduced with permission.⁸⁷ Copyright 2018 WILEY-VCH Verlag GmbH & Co. KGaA.

Nitroxyl free-radical compounds with free radicals as the redox-active centers are a known and well demonstrated option for organic cathodes in aqueous rechargeable battery systems. The nitroxyl radical, 2,2,6,6-tetramethylpiperidiny-N-oxyl (TEMPO), undergoes a one-electron oxidation process to produce an oxoammonium cation (Fig. 8a), and the positive charge is counterbalanced by taking an anion from the surrounding electrolyte.⁸⁸ Perticarari *et al.* evaluated a commercially available compound, 4-hydroxy TEMPO benzoate (4HT-benzene), as the cathode (Fig. 8b) with a bipyridinium–naphthalene diimide oligomer (DNVBr) as the anode in a highly concentrated electrolyte (8M NaClO₄) in aqueous NIBs (Fig. 8c). DNVBr was chosen as the anode because it has multi-functional groups, which are able to release and store both anions and cations. The 4HT-benzene/DNVBr full cell represents a novel aqueous battery system, operating simultaneously in an anion-rocking chair manner and a dual-ion manner. The full cell delivered an average voltage of 0.96 V with an areal capacity of 5.3 mA h cm⁻² at a C rate for 500 cycles, demonstrating a superior all-organic aqueous battery system.

Polyimides, which are a type of carbonyl group-based OEMs, are widely used in non-aqueous NIBs because of their negligible solubility, high structure tunability, and high cyclic stability. The high performance of polyimides in non-aqueous NIBs is extended to aqueous NIBs. By designing and synthesizing polyimide skeletons from dianhydride and diamine monomers, a number of research groups have achieved high-performance polyimides for aqueous NIBs.⁸⁹ Qin

et al. presented a 1,4,5,8-naphthalenetetracarboxylic dianhydride (NTCDA) derived polyimide as an anode in aqueous NIBs (Fig. 8d).⁹⁰ Upon Na^+ ion insertion/extraction, intramolecular electron transfer occurs in the polyimide. The polymer framework remains intact during the cycling, granting the polyimide material great structural stability and fast reaction kinetics. The NTCDA-based polyimide anode in the 5 M NaNO_3 aqueous electrolyte delivered discharge/charge capacities of 184 mA h g^{-1} and 165 mA h g^{-1} in aqueous NIBs (Fig. 8e). When paired with a NaVPO_4F cathode, a full cell was assembled and exhibited an initial capacity of 40 mA h g^{-1} in the first cycle and 30 mA h g^{-1} after 20 cycles (Fig. 8f).

Deng *et al.* explored a redox-active water-insoluble polyimide, poly-(naphthalene-4-formyl ethylene diamine) (PNFE), synthesized from NTCDA and ethylenediamine.⁹¹ The reaction mechanism of the PNFE electrode involves a reversible two-electron redox reaction of the polyimide (Fig. 8g), exhibiting two reduction peaks at -0.55 V and -0.9 V and two oxidation peaks at -0.75 V and -0.25 V vs. Ag/AgCl in figure 8h. PNFE delivered a high capacity of 140 mAh g^{-1} at 1 C (100 mA g^{-1}) when cycled between -1.0 V and 0 V . When the current density was increased to 12 C ($1,200 \text{ mA g}^{-1}$), the reversible capacity of PNFE dropped from 134 mA h g^{-1} to 112 mA h g^{-1} . At the high rate of 18 C ($1,800 \text{ mA g}^{-1}$), the cell still retained a reversible capacity of $\sim 95 \text{ mA h g}^{-1}$. When evaluated for long-term stability at 10 C ($1,000 \text{ mA g}^{-1}$), PNFE demonstrated high Coulombic efficiency with virtually no capacity loss over 1,000 cycles (Fig. 8i). Dong *et al.* also investigated the same NTCDA-derived polyimide, named PNTCDA.⁹² Their research focused on PNTCDA as the anode and a unique aqueous cathode dependent upon the reversible redox reactions of I^-/I^{3-} couple in a liquid (NaNO_3) cathode (Fig. 8j). As shown in figure 8j, during charging, I^- ions are oxidized to I^{3-} ions, while Na -ions are simultaneously diffused across the ion exchange separator and react with PNTCDA to form Na_x -polyimide through the enolization

process $(\text{C}=\text{O})_n \rightarrow (\text{C}-\text{O}-\text{Na})_n$. An aqueous full cell based on a solid-state PNTCDA anode and a liquid-state I^-/I_3^- cathode was assembled and evaluated. The cell delivered a reversible capacity of 95 mA h g^{-1} at 110C ($20,000 \text{ mA g}^{-1}$), and a reversible capacity of 28 mA h g^{-1} at 550C ($100,000 \text{ mA g}^{-1}$). This unique cell system further exhibited high cyclic stability over 50,000 cycles at 27C ($5,000 \text{ mA g}^{-1}$) with 70% capacity retention (Fig. 8k), demonstrating a supercapacitor-like high-rate performance and an ultra-long cycle life.

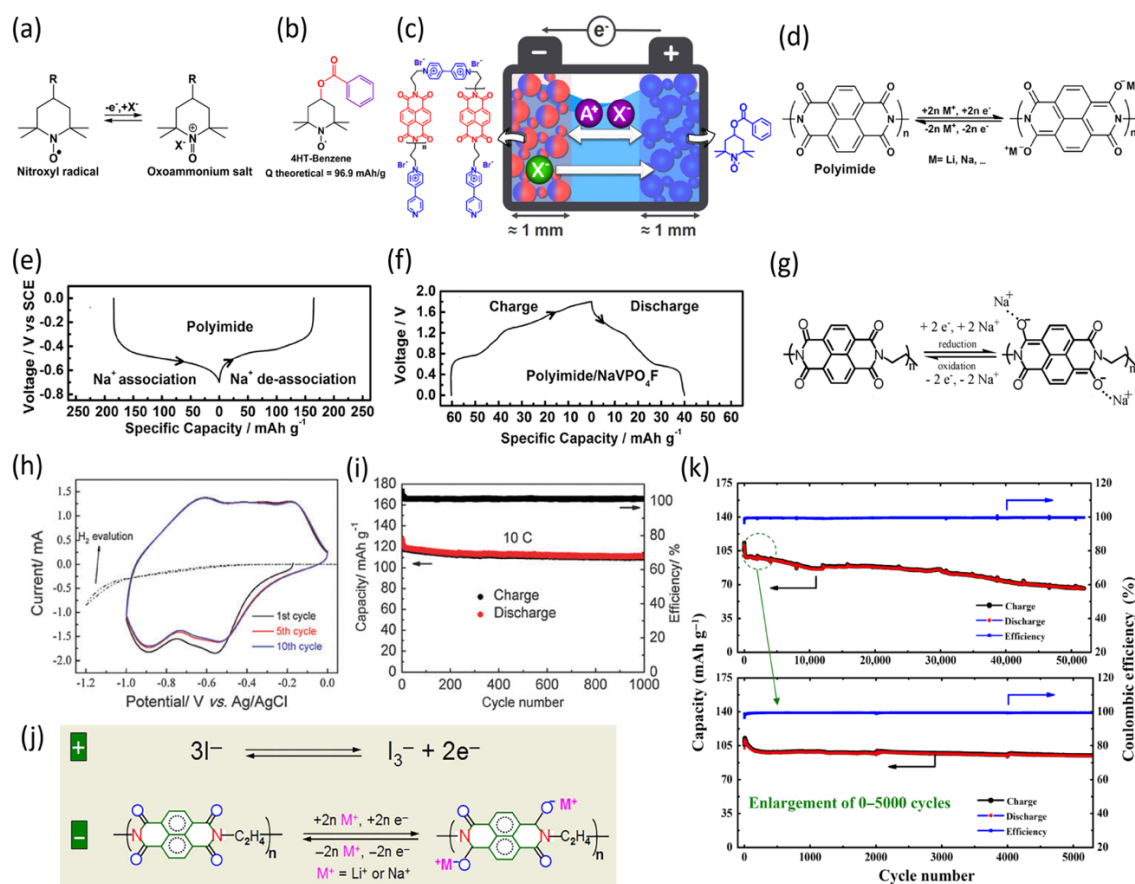


Figure 8. (a) Schematic of the redox reaction of TEMPO derivatives, (b) Structure of TEMPO derivative, 4HT-benzene. (c) Schematic of 4HT-benzene|DNVBr full cell in 8 M NaClO₄. Reproduced with permission.⁸⁸ Copyright 2019 American Chemical Society. (d) Reaction mechanism of NTCDA. Discharge-charge curves of (e) NTDCA electrode and (f) NTDCA|NaVPO₄F full cell in 5 M NaNO₃ at 50 mA g^{-1} . Reproduced with permission.⁹⁰ Copyright

2013 Elsevier B.V. (g) Reaction mechanism of PNFE. (h) Cyclic voltammetry (CV) curves (10 mV s^{-1}) demonstrating reduction and oxidation peaks. (i) Long-term cycling stability of full PNFE cell at 10 C (1.0 V – 0 V voltage window). Reproduced with permission.⁹¹ Copyright 2015 The Royal Society of Chemistry. (j) Mechanism of reversible redox reactions of I^-/I^{3-} for PNTCDA. (k) Cycle life of full cell with PNTCDA anode and liquid cathode I^-/I^{3-} . Reproduced with permission.⁹² Copyright 2016 American Association for the Advancement of Science.

In addition to carbonyl compounds, conjugated imine compounds have also demonstrated high specific capacities and superb cycling performance in aqueous NIBs attributed to the reversible reaction between imine compounds and cations, occurring at the conjugated C=N bonds.⁹³ Phenazine (PNZ), a conjugated imine compound, possesses a high theoretical specific capacity of 290 mA h g^{-1} in aqueous batteries. It was found that PNZ was insoluble in highly concentrated alkaline electrolytes, making it an attractive anode material for aqueous NIBs. Therefore, PNZ was evaluated by Sun *et al.* as an anode material in aqueous rechargeable batteries with different charge carriers, Li^+ , Na^+ , and K^+ (Fig. 9a). A full cell utilizing a PNZ anode, a $\text{Na}_{0.44}\text{MnO}_2$ (NMO) cathode, and a 10 M NaOH electrolyte was assembled and evaluated. It was demonstrated that rapid kinetics of the redox reaction of PNZ in the highly concentrated alkaline electrolyte can be achieved. The cell delivered a reversible capacity of 176 mA h g^{-1} at 4C (1,200 mA g^{-1}) with an excellent cycle life of 13,000 cycles and exhibited a fast-charging capability up to 100C (Fig. 9b and 9c). More importantly, the PNZ-NMO full cell can be cycled in a wide temperature range from $-20\text{ }^\circ\text{C}$ to $70\text{ }^\circ\text{C}$, indicating great application potential. Penticarari *et al.* explored a bipolar organic material with both n-type naphthalene tetracarboxylic diimide (NDI) and p-type viologen (Violo) moieties in one molecule to further increase the performance of

OEMs.⁹⁴ The NDI was combined with a Violo moiety to create a new compound, named MNV, which can undergo two sets of electrochemical reactions with both cations and anions. The theoretical capacity of 70 mA h g^{-1} can be achieved by MNV upon 3-electron reduction of the two Violo (Violo^{2+}) units to a viologen radical ($\text{Violo}^{\bullet+}$) and the naphthalene diimide core from (NDI) to ($\text{NDI}^{\bullet-}$) radicals (Fig. 9d). In the aqueous batteries, it was determined that the initial 1/3 of the capacity from MNV corresponded to the mixed p/n-type redox behavior of both the Violo and NDI cores, leading to a dual cation/anion insertion mechanism, while the remaining 2/3 of the capacity was attributed to the Violo moiety and the associated insertion/extraction of solvated anions. Though the specific capacity of MNV is not high, this work provides a new strategy to design advanced OEMs for aqueous NIBs.

Another type of imine compounds for aqueous NIBs is alloxazine (ALO), which has gained great success in non-aqueous LIBs and NIBs. Zhong *et al.* explored its application in aqueous NIBs with a hydrogel electrolyte and carbon-coated $\text{Na}_3\text{V}_2(\text{PO}_4)_3$ (NVP@C) as a cathode.⁹⁵ ALO has a high theoretical capacity of 250 mA h g^{-1} . However, a major challenge in its application is the severe dissolution of sodiated ALO in H_2O and poor electrical conductivity of ALO. To address the conductivity challenge, the addition of the conductive carbon (CMK-3) to fabricate the ALO/CMK-3 anode remarkably enhance the conductivity of the organic anode. To curb the dissolution challenge, polyacrylamide hydrogel electrolyte was investigated. An ideal solid content of 60% hydrogel was determined to inhibit the dissolution of sodiated ALO in H_2O , thereby increasing the electrochemical performance. Hence, a full cell was assembled using a NVP@C cathode, an ALO/CMK-3 anode, and the 60 % solid content hydrogel electrolyte (Fig. 9e). The full cell exhibited a pair of redox peaks at 1.19 V and 1.03 V in cyclic voltammogram (Fig. 9f). In the rate capability and galvanostatic charge/discharge test, a high-rate capability of

146 mA h g⁻¹ at 10C (1 C = 250 mA g⁻¹) and good capacity retention of 90% after 100 cycles at 2C were achieved (Fig. 9g and 9h). Compared to the electrochemical performance of bare ALO, the significantly improved performance of ALO/CMK-3 composite demonstrates the success of the conductive carbon on the enhancement of rate capability and cycle life of OEMs in aqueous NIBs.

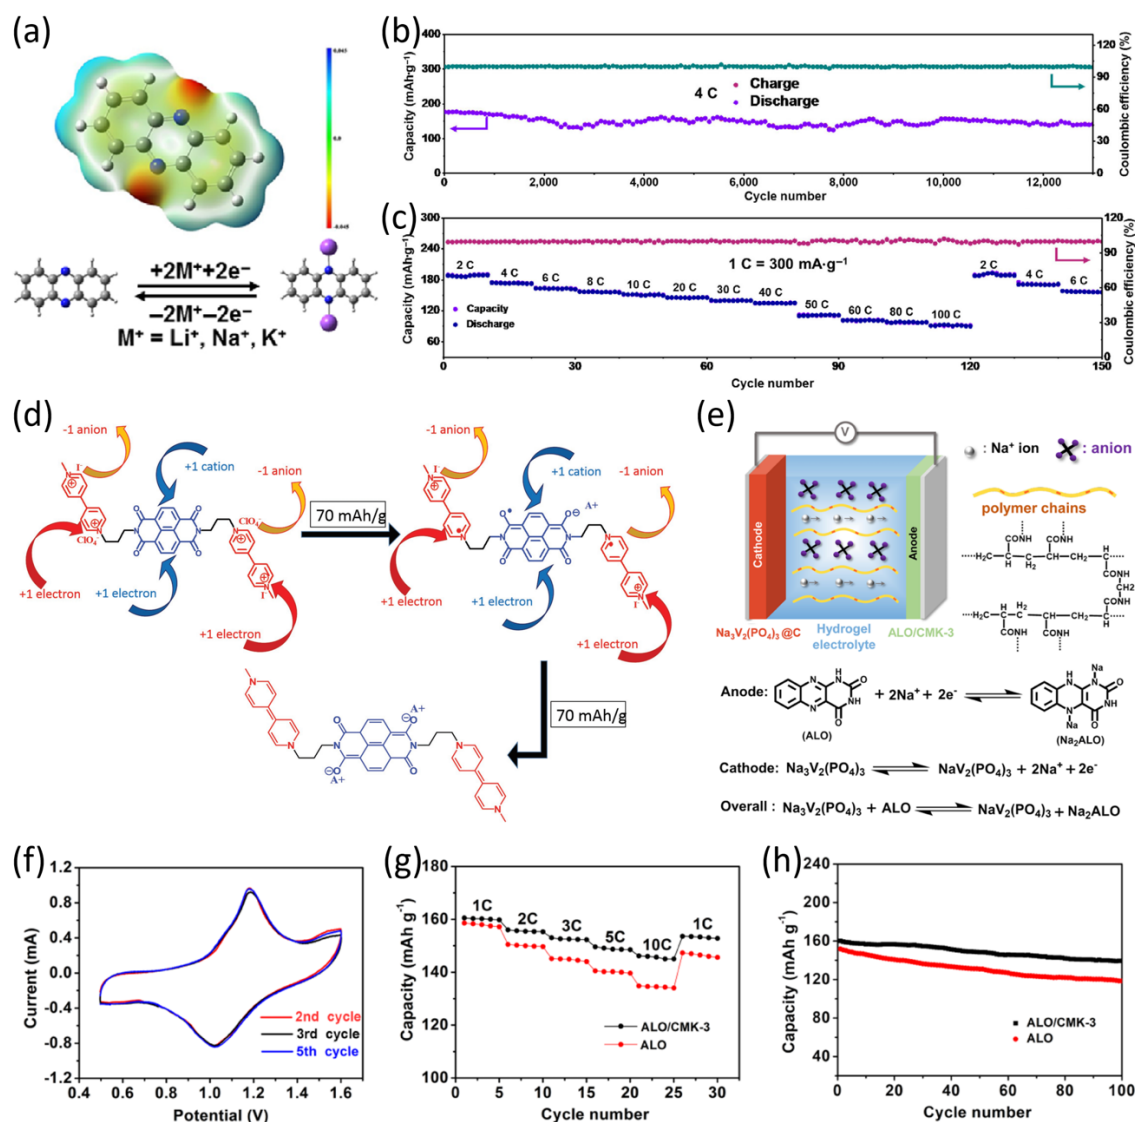






Figure 9. (a) Reaction mechanism of PNZ and molecular potential energy surface diagram. (b) Long-term cycling performance of PNZ/NMO full cell in 10M NaOH at 4 C. (c) Reversible rate

capability profiles of PNZ/NMO full cell in 10M NaOH. Reproduced with permission.⁹³ Copyright 2020 Springer Nature. (d) Anticipated electrochemistry of MNV in an aqueous electrolyte. Reproduced with permission.⁹⁴ Copyright 2017 WILEY-VCH Verlag GmbH & Co. KGaA. (e) Diagram and mechanism of the full cell ALO/CMK-3|polyacrylamide hydrogel electrolyte|NVP@C. (f) CV curves of the full cell demonstrating reduction and oxidation peaks, (g) Rate performance of the full cell, (h) Cycling profiles at 2 C for the full cell. Reproduced with permission.⁹⁵ Copyright 2018 American Chemical Society.

4. OEMs in all-solid-state NIBs

Optimization of the electrochemical performance of OEMs in NIBs has been pursued through tailoring the molecular structure, carbon encapsulation, electrolyte optimization, organic salt formation, and polymerization. However, these methods still cannot overcome all the challenges of OEMs in NIBs, including low electrical conductivity, low cyclic stability, and high solubility in conventional liquid electrolytes.⁹⁶ To search for advanced techniques to circumvent these challenges, all-solid-state battery technology, which can ultimately solve the high solubility challenge, has been explored. Recently, all-solid-state NIBs (ASSNIBs) based on OEMs were exploited by combining an organic cathode with an inorganic/organic anode in the presence of a solid-state electrolyte. Improved cyclability, capacity, and efficiency have been achieved in organic ASSNIBs. This section discusses recent advances in developing OEMs in ASSNIBs in detail. Table 4 summarizes the chemical structure and electrochemical performance of state-of-the-art OEMs in ASSNIBs.

Table 4. Summary of OEMs for all-solid-state NIBs.

Compound	Structure	Electrolyte	Average discharge voltage	Initial reversible capacity at current density	Cycle life (n)	Rate capability
PAQS ^{97*}		5 mol% NaClO ₄ -SCN PCE solid-state electrolyte	~1.9 V	205 mA h g ⁻¹ at 50 mA g ⁻¹	50	120 mA h g ⁻¹ at 800 mA g ⁻¹
Na ₂ C ₆ O ₆ ^{98*}		Na ₃ PS ₄ solid-state electrolyte	~2.0 V	182 mA h g ⁻¹ at 20 mA g ⁻¹	400	94 mA h g ⁻¹ at 0.5C
PTO ^{99,100*}		Na ₃ PS ₄ solid-state electrolyte	~2.0 V	376 mA h g ⁻¹ at 0.01C	500	200 mA h g ⁻¹ at 1C
		Beta-alumina solid electrolyte (BASE)	~2.4 V	362 mA h g ⁻¹ at 0.1C	50	180 mA h g ⁻¹ at 0.5C
P(AN-NA) ^{97*}		5 mol% NaClO ₄ -SCN PCE solid-state electrolyte	~3 V	120 mA h g ⁻¹ at 50 mA g ⁻¹	50	120 mA h g ⁻¹ at 800 mA g ⁻¹

Note: *The electrochemical performances of the OEMs are collected from the full-cell data, because the half-cell data were not reported.

4.1 All-organic ASSNIBs

In an effort to explore the impact of utilizing n-type and p-type polymers in ASSNIBs, Zhu *et al.* fabricated all-organic ASSNIBs composed of poly(anthraquinonyl sulfide) (PAQS) as the anode and poly(aniline/*o*-nitroaniline) (P(AN–NA)) as the cathode and a plastic crystal electrolyte (PCE) based on succinonitrile ($\text{N}\equiv\text{C}-\text{CH}_2-\text{CH}_2-\text{C}\equiv\text{N}$, SCN) and NaClO_4 as the solid electrolyte (Na^+ -PCEs).⁹⁷ The Na^+ -PCEs were formed by dissolving ionic salts in a polar organic molecular solid and were developed for use in rechargeable Li batteries, fuel cells, and dye-sensitized solar cells. However, their application in NIBs was rare. The prepared Na^+ -PCEs exhibited a high ionic conductivity of $\sim 10^{-3} \text{ S cm}^{-1}$ at ambient temperature, comparable with liquid electrolytes in non-aqueous NIBs. Additionally, it displayed a plastic phase in a wide temperature range ($-35 \text{ }^\circ\text{C}$ to $62 \text{ }^\circ\text{C}$), a wide electrochemical window ($1.3 \text{ V} - 4.9 \text{ V}$ vs. Na/Na^+), and good mechanical flexibility, indicating great promise for ASSNIBs. Redox-active polymers, PAQS and P(AN–NA), represent n-type and p-type OEMs, respectively. During the battery charge process, PAQS anode accepts electrons from the external circuit and Na^+ ion insertion occurs, while the P(AN–NA) cathode is electrochemically oxidized, releasing its electrons to the external circuit with “p-doping” of ClO_4^- anions into the cathode host. This unique cell exhibits symmetric charge/discharge curves with a sloping voltage output from $0.8 \text{ V} - 2.6 \text{ V}$ (Fig. 10a) and a reversible capacity of 200 mA h g^{-1} (determined by the PAQS anode). It retains a reversible capacity of 160 mA h g^{-1} over 50 cycles with 80% capacity retention. Furthermore, the all-organic ASSNIBs demonstrate 60% capacity retention even when cycled at a high current density of 800 mA g^{-1} (Fig. 10b), which is comparable to reported rate performances of non-aqueous NIBs.

4.2 Organic ASSNIBs based on inorganic solid-state electrolytes

In addition to the PCEs, other inorganic solid-state electrolytes were also used in organic ASSNIBs. Chi *et al.* fabricated a symmetric all-solid-state battery utilizing an organic salt, $\text{Na}_4\text{C}_6\text{O}_6$ (Fig. 10c) as both the anode and cathode, and a sulfide-based solid-state electrolyte, Na_3PS_4 (NPS).⁹⁸ Sulfide electrolytes are promising electrolyte alternatives due to their high ionic conductivity, but they suffer from a narrow stability window (1.5 V – 2.7 V vs. Na^+/Na) and are prone to forming resistive interfacial layers when high-voltage cathodes or Na metal anodes are used. To address this interfacial challenge, the cell system was cycled within the stability window of NPS. The organic ASSNIBs using $\text{Na}_4\text{C}_6\text{O}_6$ as a cathode with a $\text{Na}_{14}\text{Sn}_4$ anode, demonstrated good performance with a reversible capacity of 140 mA h g^{-1} (76% capacity retention) at 0.1 C (20 mA g^{-1}) for 100 cycles and 107 mA h g^{-1} (70% capacity retention) at 0.2 C (40 mA g^{-1}) for 400 cycles, representing the record cycling performance reported to date for ASSNIBs.⁹⁸ $\text{Na}_4\text{C}_6\text{O}_6$ contains two phenolate groups and two carbonyl groups that can participate in the electrochemical redox reactions in both cathode and anode. The two phenolate groups act as active centers in the cathode to provide 2 sodium ions at high potentials, while two carbonyl groups can act as active centers in the anode to store additional 2 sodium ions at low potentials. The symmetric organic ASSNIBs using $\text{Na}_4\text{C}_6\text{O}_6$ as both the cathode and anode (Fig. 10d) demonstrated stable cycling performance at 0.1 C (20 mA g^{-1}) for 50 cycles with 66% capacity retention. This work successfully developed an OEM as both the cathode and anode that is compatible with sulfide-based solid-state electrolytes in ASSNIBs.

Chi *et al.* also developed an organic ASSNIBs based on pyrene-4,5,9,10-tetraone (PTO), a quinone-based compound, as the cathode material.⁹⁹ PTO was selected because it contains four carbonyl groups capable of storing four cations and shows a high capacity of 409 mA h g^{-1} (Fig.

10e). However, PTO is known to suffer from the dissolution challenge and shuttling reaction in liquid electrolytes, causing rapid capacity decay. To remedy this challenge, the PTO cathode was paired with an oxide-based solid-state electrolyte, the beta-alumina solid electrolyte (BASE), which exhibits high electrochemical stability in a voltage window of 0 V – 3.5 V vs. Na⁺/Na. The rigid surface of BASE poses a challenge during the formation of interfacial layers between PTO and sodium metal, resulting in high interfacial resistance, poor cycle life, and fluctuating voltage profiles. Hence, a Sn layer was deposited via thermal evaporation onto the rigid surface of BASE, lowering surface roughness and surface tension of sodium metal, increasing the wettability, and improving ionic/electronic conductivity for Na plating/stripping (by forming ‘sodiophobic to sodiophilic contact’) (Fig. 10f).⁹⁹ Furthermore, to address the interfacial barrier issues at the cathode and electrolyte interphase (causing poor ionic transport), a PTO-poly(ethylene oxide) (PEO) composite cathode was fabricated, in which PEO served to increase interfacial contact between the cathode and BASE. With these improvements, a full cell, Na|Sn|BASE|PTO-PEO, was assembled and demonstrated an initial energy density of ~900 Wh kg⁻¹ and an average voltage of 2.46 V vs Na/Na⁺ (Fig. 10g).

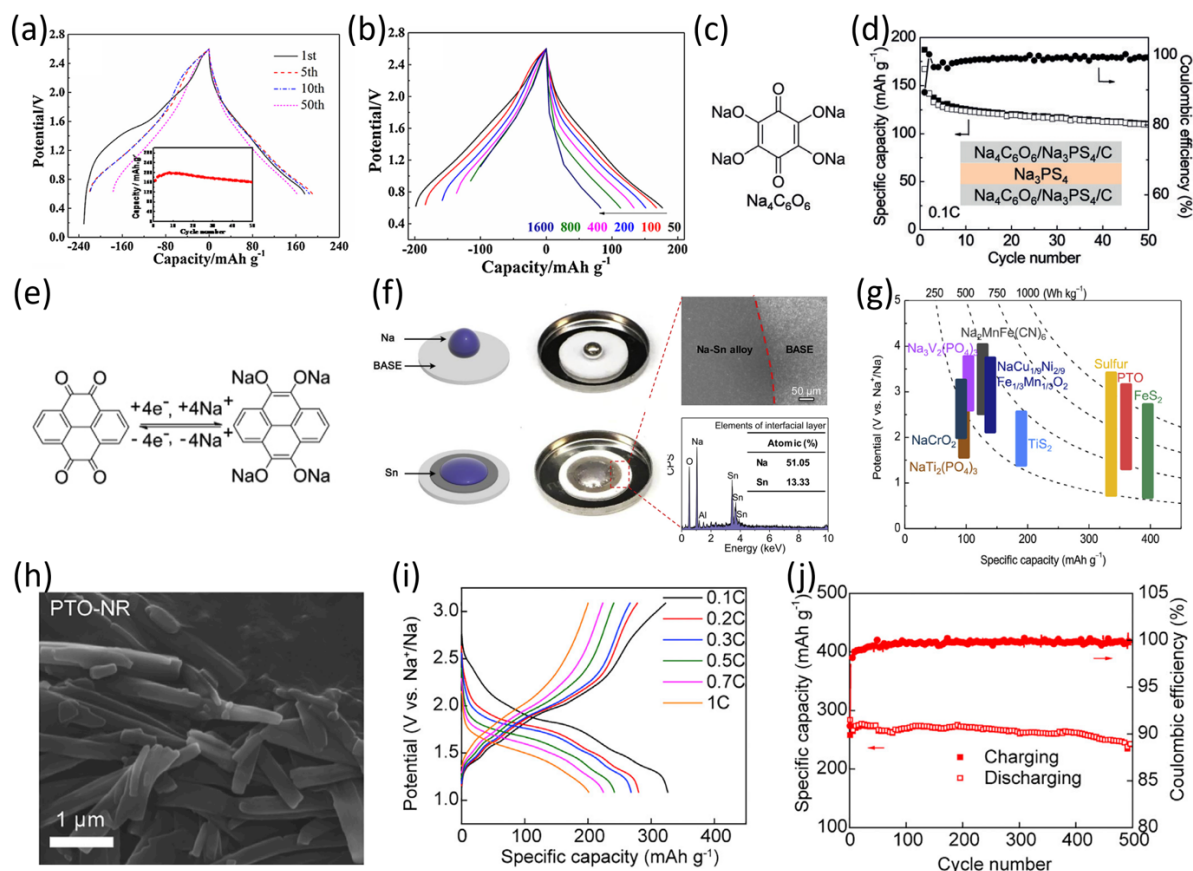


Figure 10. (a) Discharge-charge profiles for PAQS/P(AN-NA) cell at 50 mA g⁻¹ (0.8 V – 2.6 V voltage window), (inset 10a) cycling curve of capacity versus cycle number for PAQS/P(AN-NA), (b) Discharge-charge profiles for PAQS/P(AN-NA) at different current densities. Reproduced with permission.⁹⁷ Copyright 2015 Elsevier Ltd. (c) Structure of Na₄C₆O₆, organic salt anode-cathode material. (d) Cycling of a symmetric Na₄C₆O₆/Na₃PS₄/Na₄C₆O₆ full cell (Inset: cell schematic). Reproduced with permission.⁹⁸ Copyright 2018 Wiley-VCH Verlag GmbH & Co. KGaA. (e) Structure and mechanism of PTO. (f) Sn layer deposited via thermal evaporation onto the surface of BASE. (g) A comprehensive survey of the redox potentials and experimentally demonstrated specific capacities of all-solid-state full cells with sodium metal anodes and various cathodes. Reproduced with permission.⁹⁹ Copyright 2019 Elsevier Ltd. (h) SEM imaging of PTO-NR demonstrating 1 μm sizing, (i) Galvanostatic voltage profiles of PTO-NR at different C rates (1 C

= 409 mA g⁻¹), (j) Capacity and CE % versus cycle number for PTO-NR-based cell at 0.3 C. Reproduced with permission.¹⁰⁰ Copyright 2019 Elsevier Inc.

Although the PTO cathode exhibited high energy density in ASSNIBs, its cyclic stability is limited by the BASE electrolyte. To further improve its cycle life, PTO was coupled with Na₃PS₄, a sulfide-based solid-state electrolyte in ASSNIBs.¹⁰⁰ The PTO cathode was optimized by creating a PTO-carbon composite with 10 wt% carbon, resulting in an initial charge capacity of 314 mA h g⁻¹, the first-cycle Coulombic efficiency of 82%, and 93% capacity retention after 20 cycles. In contrast, the bare PTO cathode only delivered a specific capacity of ~200 mA h g⁻¹ (49% of its theoretical capacity) with the first-cycle Coulombic efficiency of 75%. Therefore, carbon plays an essential role in improving the electrochemical performance of the PTO cathode. To further evaluate the interfacial challenge between the cathode and electrolyte interface, *in-situ* electrochemical impedance spectroscopy (EIS) measurements were performed and determined a reversible interfacial resistance evolution during cycling for the first time. This reversible behavior is attributed to the conversion between the conductive Na₃PS₄ phase and resistive phases within the operating voltage window of PTO (1.1 V – 3.1 V vs. Na⁺/Na). Moreover, PTO with low modulus maintains intimate interfacial contact with solid electrolytes during cycling, improving the cyclic stability of ASSNIBs. PTO-nanorods (PTO-NRs) were prepared via antisolvent precipitation method to reduce the particle size from an average diameter of 5 μm and a thickness of 1 μm to ~1 μm in length and ~300 nm in thickness, shortening the ionic and electronic pathways, increasing reaction kinetics, and improving battery performance. PTO-NRs based ASSNIBs delivered specific energy of 587 W h kg⁻¹ at 0.1C and 335 W h kg⁻¹ at 1C with 89% capacity retention for 500 cycles at 0.3C (Fig. 10h-j), representing the best electrochemical performance in

organic ASSNIBs so far. The exceptional performance of OEMs opens up a new door for the development of ASSNIBs towards the direction of cost-effective and sustainable energy storage devices.

5. Summary and outlook

OEMs are extensively used in non-aqueous, aqueous, and all-solid-state NIBs due to flexible structural tunability and the abundant nature of organic compounds and polymers. This review summarized recent advances in developing OEMs as cathode and anode materials in various NIBs, as well as the correlation between molecular structure and electrochemical performance for rational structure design and performance optimization. Figure 11 shows the application of advanced OEMs in various NIBs and emphasizes the functional groups that are used in each type of NIBs. To date, considerable research efforts have been devoted to developing OEMs in NIBs, and significant achievements have been obtained. A rich variety of approaches such as tailoring molecular structures, extending π conjugated structure, self-healing chemistry, fabricating composite structure with carbon, organic salt formation, and polymerization, are utilized to overcome the three challenges of OEMs in NIBs (low conductivity, high solubility, and particle pulverization). As discussed throughout this review, a rich variety of approaches have been utilized to overcome the high-solubility challenge of OEMs in liquid electrolytes to improve the specific capacity, Coulombic efficiency, and cycling stability of OEMs in NIBs.

- (1) Surface modification: Depositing a thin and dense layer of insoluble compounds such as Al_2O_3 on organic electrodes can physically block the contact between OEMs and liquid electrolytes to prevent the dissolution. This thin and dense layer will not only mitigate the dissolution of OEMs but also act as an artificial SEI to protect the interphase of organic electrodes, and thus

improve the performance of OEMs. However, the thickness of this thin layer needs to be precisely controlled because it could enhance the interphasial resistance and reduce the reaction kinetics of organic electrodes.

- (2) Polymerization: Increasing the molecular weight to generate polymers decreases solubility by altering the polarity of OEMs. The molecular weight of repeating units in polymers determines the theoretical capacity of polymeric electrode materials, so the inactive branches and functional groups introduced into the polymer repeating units could reduce the solubility but will compromise the electrochemical performance, in terms of low specific capacity and sluggish reaction kinetics. Rational structure design for polymeric electrode materials is required to optimize the capacity, cycle life, and rate capability.
- (3) Salinization (Organic salt formation): Salinization by synthesizing organic salts converts the covalent bonds in OEMs to ionic bonds, which remarkably enhance their polarity and reduce their solubility. Salinization has been proved to be an effective method to improve the cyclic stability of OEMs while still maintaining low molecular weights for high theoretical specific capacities. More importantly, unlike most organic cathodes without sodium sources, the organic sodium salts based on rational structure design can act as pre-sodiated cathodes to couple with various sodium-free anodes for all-organic sustainable batteries.
- (4) Hybridization: Hybridizing OEMs with insoluble inorganic materials is an effective strategy to reduce solubility. There are three effective methods to stabilize OEMs by hybridization: 1) confining the OEMs into the small pores of porous materials such as porous carbon; 2) using the $\pi - \pi$ interaction between conjugated OEMs and conjugated inorganic materials such as graphene or carbon nanotube; 3) forming chemical bonding such as covalent or ionic bonds to chemically attach OEMs to inorganic materials or ions to provide organic/inorganic

composites or metal-organic frameworks. Hybridization could reduce the solubility and improve the cycle life of OEMs, but the use of a large amount of inactive inorganic materials decreases the capacity and energy density of organic electrodes.

(5) Electrolyte optimization: Liquid electrolytes play a critical role in the electrochemical performance of OEMs. Manipulating the electrolyte composition could significantly change the chemical/physical properties of the electrolytes to reduce the solubility of OEMs. The polarity and donor ability of electrolytes can be optimized by tuning the sodium salt concentration, altering the anions in sodium salts and the structure of organic solvents, using ionic liquids and other additives. In addition to low OEMs solubility, the optimized electrolytes should retain high Na-ion conductivity, high Na-ion transference number, and low viscosity.

To date, advanced OEMs have been obtained to achieve high specific capacities ($> 200 \text{ mA h g}^{-1}$), long cycle life ($> 1,000$ cycles), and fast-charging capability (up to 100C). However, there are still two challenges for the practical application of OEMs in NIBs: 1) low mass loading; 2) flooded electrolyte condition. Most reported organic NIBs use a low mass loading ($1\sim 3 \text{ mg cm}^{-2}$) of OEMs in the electrodes because the thinner electrodes exhibit faster reaction kinetics and higher specific capacity. However, the areal capacity and energy density of OEMs, which are more important in practical applications, are lower than that of the inorganic counterparts. To improve the energy density of OEMs in NIBs, it is of great significance to enhance the mass loading of OEMs in the electrodes to 10 mg cm^{-2} or higher to assess their electrochemical performance. The battery performance at a high mass loading is vital for the development of OEMs. In addition, the flooded electrolyte condition ($>50 \mu\text{L}_{\text{electrolyte}}/\text{mg}_{\text{active material}}$) is widely used to measure the electrochemical performance of OEMs in NIBs, because it facilitates the reaction kinetics and improves the cycle life. Nevertheless, the lean electrolyte condition ($3\sim 5 \mu\text{L}_{\text{electrolyte}}/\text{mg}_{\text{active material}}$)

is used in the commercial rechargeable batteries to improve the energy density of the battery. Commercial NIBs based on OEMs will also use the lean electrolyte condition, thus the electrochemical performance of OEMs at a high mass loading and lean electrolyte condition should be emphasized in the research.

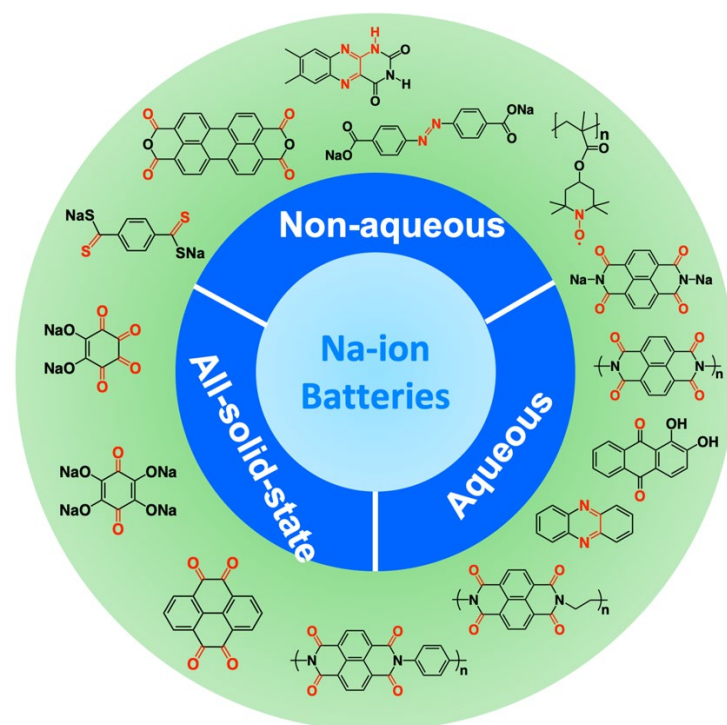


Figure 11. The schematic illustration for the application of representative OEMs in non-aqueous, aqueous, and all-solid-state NIBs.

Due to the different nature of non-aqueous, aqueous, and all-solid-state NIBs, the targeted performance improvement strategies for each type of battery are distinct. For example, quinones and polyimides act as cathode materials in non-aqueous NIBs but are anode materials in aqueous NIBs, so their redox potentials should be increased in non-aqueous NIBs but decreased in aqueous NIBs by rational structure design to improve their electrochemical performance. More importantly, non-aqueous and aqueous electrolytes show completely different polarity and donor abilities,

resulting in different OEMs solubility. The all-solid-state electrolytes overcome the high-solubility challenge but suffer from poor interphasial contact and low electrode-electrolyte compatibility. Therefore, the targeted performance improvement strategies for each type of battery are different. Herein, the targeted strategies are summarized and described as follows:

- (1) In non-aqueous NIBs, the organic liquid electrolytes exhibit wide stability windows, which enable the use of a rich variety of OEMs. For instance, carboxylate compounds, azo compounds, and Schiff base are anode materials, while quinones, polyimides, and p-type OEMs are cathode materials. Electron-donating functional groups could be introduced into anode materials to reduce the redox potentials, and electron-withdrawing functional groups could be attached to cathode materials to enhance the redox potentials. Surface modification, polymerization, salinization, hybridization, and electrolyte optimization are used to mitigate the solubility of OEMs. The poor conductivity, particle pulverization, and high solubility challenges can be overcome by rational molecular, composite, and electrolyte structure design to improve the conductivity, integrity, and stability of organic electrodes.
- (2) In aqueous NIBs, the aqueous electrolytes exhibit narrow stability windows due to the electrochemical water splitting, so low-redox-potential OEMs such as carboxylate compounds, azo compounds, and Schiff base cannot be used in anodes, while high-redox-potential OEMs such as quinones and polyimides are used as anode materials to couple with p-type organic cathodes or inorganic cathodes. Moreover, the polarity of water is higher than organic solvents, so salinization is not a proper method to reduce the water-solubility of OEMs. Extending the hydrophobic backbone structure and polymerization are effective methods to mitigate the dissolution of OEMs in aqueous electrolytes. Surface modification and hybridization could

meliorate the interphase stability and conductivity of organic electrodes to further improve the electrochemical performance in terms of long cycle life and fast reaction kinetics.

- (3) In all-solid-state NIBs, the high-solubility challenge is not present, but the poor interphasial contact and low electrode-electrolyte compatibility become the main hurdles. Therefore, accommodating the large volume change and improving the structural stability are critical for OEMs. Tailoring the molecular structure of OEMs to enhance the stability and compatibility with solid-state electrolytes is vital for organic all-solid-state NIBs. In addition, surface modification and hybridization can also be used to accommodate the large volume change and enable intimate contact between electrode materials and electrolytes.

Although the development of OEMs in NIBs is slower than LIBs and other inorganic battery systems, the substantial demand for cost-effective and sustainable energy storage devices attracts massive research interests and efforts to develop high-performance OEMs for NIBs. Due to the universal nature of OEMs in alkali-ion batteries, the promising methods for structure design and performance optimization could draw inspiration from the success of OEMs in LIBs. For instance, the capacity and redox potential of OEMs can be enhanced by incorporating multi-functional groups in one organic framework.¹¹⁷ More research efforts are demanded to further boost the battery performance of OEMs. To shed light on the development of advanced OEMs in non-aqueous, aqueous, and all-solid-state NIBs, we outline future research directions of OEMs in each type of NIBs as follows.

- (1) **Non-aqueous NIBs:** The main obstacles to developing OEMs in non-aqueous NIBs are the high solubility in the electrolyte and slow reaction kinetics. To circumvent these challenges and achieve high-stability and fast-charging batteries, it is pivotal to develop new structures for electrode materials and electrolytes. For example, the highly conductive 3D porous

substrates such as porous graphene films or porous copper/aluminum current collectors can be used to encapsulate OEMs in the porous structures and reduce the amount of conductive carbon in the organic electrodes, resulting in improved cyclic stability, energy density, and rate capability. In addition, the new electrolytes based on fluorinated solvents, high concentration sodium salts, ionic liquids, etc. are demanded to construct a stable and robust SEI layer to protect OEMs upon long-term cycling. The molecular structure of OEMs can also be optimized by manipulating the functional groups, heteroatoms, structure isomerism, and material porosity for high-performance, cost-effective, and sustainable non-aqueous NIBs.

(2) **Aqueous NIBs:** Due to the narrow voltage window of the aqueous electrolytes, a number of high-performance inorganic electrode materials and OEMs in non-aqueous NIBs cannot be used in aqueous NIBs. An important task for the development of aqueous NIBs should be enlarging the voltage window of the aqueous electrolytes and mitigating electrochemical water splitting at high and low potentials. The water-in-salt electrolytes and organic/inorganic additives could be used to enhance the stability of the aqueous electrolytes. Constructing a stable and robust SEI layer to avoid the continuous decomposition of the aqueous electrolyte is also very important in aqueous NIBs. Additionally, the dissolution of OEMs and sodiated OEMs in water is a challenge in aqueous organic NIBs, so polymers with large backbone structures are favorable in developing high-performance aqueous NIBs. More research efforts should be devoted to the design and synthesis of redox-active polymers for cost-effective and sustainable aqueous NIBs.

(3) **All-solid-state NIBs:** There are only a few reports about the application of OEMs in all-solid-state NIBs. The development of OEMs in all-solid-state NIBs is still in its infancy. Although the use of solid-state electrolytes avoids the dissolution of OEMs, the main challenge in all-

solid-state batteries is the poor interfacial contact, especially under large volume change. The electrochemical performance of all-solid-state NIBs is not only dependent on the performance of OEMs but also related to the stability and resistance of the interphase between OEMs and solid-state electrolytes upon long-term cycling. Developing soft, flexible, and low modulus OEMs could be an ideal solution for this challenge and enable the intimate contact between OEMs and solid-state electrolytes in all-solid-state NIBs. Therefore, the structure design and synthesis of soft, flexible, and low modulus OEMs is a potential direction for high-performance, cost-effective and sustainable all-solid-state NIBs.

The applications of advanced OEMs in non-aqueous, aqueous and all-solid-state NIBs are promising for developing cost-effective and sustainable energy storage devices. This review not only provides a comprehensive overview of state-of-the-art OEMs in various NIBs but also offers guidance for rational structure design and performance optimization of advanced OEMs. The understanding of the advantages, challenges, development, applications, and outlook of OEMs in various NIBs will attract considerable research interests and stimulate further research in these fields.

Conflicts of interest

The authors declare no conflict of interest.

Acknowledgments

This work was supported by the US National Science Foundation Award No. 2000102 and the George Mason University, College of Science Postdoctoral Fellowship. The authors also

acknowledge the support from the George Mason University Quantum Science & Engineering Center.

References

1. V. Palomares, P. Serras, I. Villaluenga, K. B. Hueso, J. Carretero-González and T. Rojo, *Energy Environ. Sci.*, 2012, **5**, 5884–5901.
2. M. D. Slater, D. Kim, E. Lee and C. S. Johnson, *Adv. Funct. Mater.*, 2013, **23**, 947–958.
3. A. Zhou, W. Cheng, W. Wang, Q. Zhao, J. Xie, W. Zhang, H. Gao, L. Xue and J. Li, *Adv. Energy Mater.*, 2020, 2000943.
4. H. Pan, Y. S. Hu and L. Chen, *Energy Environ. Sci.*, 2013, **6**, 2338–2360.
5. N. Yabuuchi, K. Kubota, M. Dahbi and S. Komaba, *Chem. Rev.*, 2014, **114**, 11636–11682.
6. L. Li, Y. Zheng, S. Zhang, J. Yang, Z. Shao and Z. Guo, *Energy Environ. Sci.*, 2018, **11**, 2310–2340.
7. F. Liu, T. Wang, X. Liu and L. Z. Fan, *Adv. Energy Mater.*, 2020, 2000787.
8. D. Larcher and J.-M. Tarascon, *Nat. Chem.*, 2014, **7**, 19–29.
9. C. Luo, A. Langrock, X. Fan, Y. Liang and C. Wang, *J. Mater. Chem. A*, 2017, **5**, 18214–18220.
10. U. Maitra, R. A. House, J. W. Somerville, N. Tapia-Ruiz, J. G. Lozano, N. Guerrini, R. Hao, K. Luo, L. Jin, M. A. Pérez-Osorio, F. Massel, D. M. Pickup, S. Ramos, X. Lu, D. E. McNally, A. V. Chadwick, F. Giustino, T. Schmitt, L. C. Duda, M. R. Roberts and P. G. Bruce, *Nat. Chem.*, 2018, **10**, 288–295.
11. C. Luo, Y. Xu, Y. Zhu, Y. Liu, S. Zheng, Y. Liu, A. Langrock and C. Wang, *ACS Nano*, 2013, **7**, 8003–8010.

12. L. Fan, R. Ma, Q. Zhang, X. Jia and B. Lu, *Angew. Chemie - Int. Ed.*, 2019, **58**, 10500–10505.
13. Z. L. Xu, G. Yoon, K. Y. Park, H. Park, O. Tamwattana, S. Joo Kim, W. M. Seong and K. Kang, *Nat. Commun.*, 2019, **10**, 2598.
14. E. M. Lotfabad, J. Ding, K. Cui, A. Kohandehghan, W. P. Kalisvaart, M. Hazelton and D. Mitlin, *ACS Nano*, 2014, **8**, 7115–7129.
15. Y. Kim, Y. Park, A. Choi, N. S. Choi, J. Kim, J. Lee, J. H. Ryu, S. M. Oh and K. T. Lee, *Adv. Mater.*, 2013, **25**, 3045–3049.
16. B. Xiao, T. Rojo and X. Li, *ChemSusChem*, 2019, **12**, 133–144.
17. Y. Wen, K. He, Y. Zhu, F. Han, Y. Xu, I. Matsuda, Y. Ishii, J. Cumings and C. Wang, *Nat. Commun.*, 2014, **5**, 4033.
18. Y. Xu, Y. Zhu, Y. Liu and C. Wang, *Adv. Energy Mater.*, 2013, **3**, 128–133.
19. Z. Hu, L. Wang, K. Zhang, J. Wang, F. Cheng, Z. Tao and J. Chen, *Angew. Chemie - Int. Ed.*, 2014, **53**, 12794–12798.
20. J. Wang, C. Luo, A. Langrock, A. C. Mignerey and C. Wang, *Small*, 2015, **11**, 473–481.
21. J. Ruan, T. Yuan, Y. Pang, S. Luo, C. Peng, J. Yang and S. Zheng, *Carbon*, 2018, **126**, 9–16.
22. F. Xiao, X. Yang, H. Wang, J. Xu, Y. Liu, D. Y. W. Yu and A. L. Rogach, *Adv. Energy Mater.*, 2020, **10**, 2000931.
23. K. Song, C. Liu, L. Mi, S. Chou, W. Chen and C. Shen, *Small*, 2019, 1903194.
24. H. Wang, Z. Tong, R. Yang, Z. Huang, D. Shen, T. Jiao, X. Cui, W. Zhang, Y. Jiang and C. S. Lee, *Adv. Energy Mater.*, 2019, **9**, 1903046.
25. E. Goikolea, V. Palomares, S. Wang, I. R. de Larramendi, X. Guo, G. Wang and T. Rojo, *Adv. Energy Mater.*, 2020, **10**, 2002055.
26. S. S. Sharma and A. Manthiram, *Energy Environ. Sci.*, 2020, **13**, 4087–4097.

27. K. B. Hueso, V. Palomares, M. Armand and T. Rojo, *Nano Res.*, 2017, **10**, 4082–4114.
28. G. Li, X. Lu, J. Y. Kim, V. V. Viswanathan, K. D. Meinhardt, M. H. Engelhard and V. L. Sprenkle, *Adv. Energy Mater.*, 2015, **5**, 1500357.
29. Y. Wang, D. Zhou, V. Palomares, D. Shanmukaraj, B. Sun, X. Tang, C. Wang, M. Armand, T. Rojo and G. Wang, *Energy Environ. Sci.*, 2020, **13**, 3848–3879.
30. C. Delmas, D. Carlier and M. Guignard, *Adv. Energy Mater.*, 2020, 2001201.
31. J. J. Shea and C. Luo, *ACS Appl. Mater. Interfaces*, 2020, **12**, 5361–5380.
32. Y. Lu, Q. Zhang, L. Li, Z. Niu and J. Chen, *Chem*, 2018, **4**, 2786–2813.
33. T. B. Schon, B. T. McAllister, P. F. Li and D. S. Seferos, *Chem. Soc. Rev.*, 2016, **45**, 6345–6404.
34. B. Häupler, A. Wild and U. S. Schubert, *Adv. Energy Mater.*, 2015, **5**, 1402034.
35. Y. Xu, M. Zhou and Y. Lei, *Mater. Today*, 2018, **21**, 60–78.
36. Q. Zhao, Y. Lu and J. Chen, *Adv. Energy Mater.*, 2017, **7**, 1601792.
37. T. Sun, J. Xie, W. Guo, D. S. Li and Q. Zhang, *Adv. Energy Mater.*, 2020, **10**, 1904199.
38. A. V. Desai, R. E. Morris and A. R. Armstrong, *ChemSusChem*, 2020, **13**, 4866–4884.
39. P. Poizot, J. Gaubicher, S. Renault, L. Dubois, Y. Liang and Y. Yao, *Chem. Rev.*, 2020, **120**, 6490–6557.
40. S. Lee, G. Kwon, K. Ku, K. Yoon, S. K. Jung, H. D. Lim and K. Kang, *Adv. Mater.*, 2018, **30**, 1704682.
41. S. Lee, J. Hong and K. Kang, *Adv. Energy Mater.*, 2020, **10**, 2001445.
42. Z. Song and H. Zhou, *Energy Environ. Sci.*, 2013, **6**, 2280–2301.
43. C. Luo, Y. Zhu, Y. Xu, Y. Liu, T. Gao, J. Wang and C. Wang, *J. Power Sources*, 2014, **250**, 372–378.

44. H. Wu, S. A. Shevlin, Q. Meng, W. Guo, Y. Meng, K. Lu, Z. Wei and Z. Guo, *Adv. Mater.*, 2014, **26**, 3338–3343.
45. M. Lee, J. Hong, H. Kim, H. D. Lim, S. B. Cho, K. Kang and C. B. Park, *Adv. Mater.*, 2014, **26**, 2558–2565.
46. X. Fan, F. Wang, X. Ji, R. Wang, T. Gao, S. Hou, J. Chen, T. Deng, X. Li, L. Chen, C. Luo, L. Wang and C. Wang, *Angew. Chemie - Int. Ed.*, 2018, **57**, 7146–7150.
47. J. Hong, M. Lee, B. Lee, D.-H. Seo, C. B. Park and K. Kang, *Nat. Commun.*, 2014, **5**, 5335.
48. M. Armand, S. Grugeon, H. Vezin, S. Laruelle, P. Ribière, P. Poizot and J.-M. Tarascon, *Nat. Mater.*, 2009, **8**, 120–125.
49. A. Jouhara, N. Dupré, A. C. Gaillot, D. Guyomard, F. Dolhem and P. Poizot, *Nat. Commun.*, 2018, **9**, 4401.
50. C. Luo, J. Wang, X. Fan, Y. Zhu, F. Han, L. Suo and C. Wang, *Nano Energy*, 2015, **13**, 537–545.
51. Y. Park, D. S. Shin, S. H. Woo, N. S. Choi, K. H. Shin, S. M. Oh, K. T. Lee and S. Y. Hong, *Adv. Mater.*, 2012, **24**, 3562–3567.
52. L. Zhao, J. Zhao, Y. S. Hu, H. Li, Z. Zhou, M. Armand and L. Chen, *Adv. Energy Mater.*, 2012, **2**, 962–965.
53. E. Castillo-Martínez, J. Carretero-González and M. Armand, *Angew. Chemie - Int. Ed.*, 2014, **53**, 5341–5345.
54. A. Abouimrane, W. Weng, H. Eltayeb, Y. Cui, J. Niklas, O. Poluektov and K. Amine, *Energy Environ. Sci.*, 2012, **5**, 9632–9638.
55. N. Ogihara, T. Yasuda, Y. Kishida, T. Ohsuna, K. Miyamoto and N. Ohba, *Angew. Chemie - Int. Ed.*, 2014, **53**, 11467–11472.

56. K. Sakaushi, E. Hosono, G. Nickerl, T. Gemming, H. Zhou, S. Kaskel and J. Eckert, *Nat. Commun.*, 2013, **4**, 1485.
57. D. Xu, M. Liang, S. Qi, W. Sun, L. Lv, F. Du, B. Wang, S. Chen, Y. Wang and Y. Yu, *ACS nano*, DOI:10.1021/acsnano.0c05896.
58. Z. Shadike, S. Tan, Q.-C. Wang, R. Lin, E. Hu, D. Qu and X.-Q. Yang, *Mater. Horizons*, 2021, DOI:10.1039/d0mh01364a.
59. C. Luo, X. Fan, Z. Ma, T. Gao and C. Wang, *Chem*, 2017, **3**, 1050–1062.
60. H. G. Wang, S. Yuan, Z. Si and X. B. Zhang, *Energy Environ. Sci.*, 2015, **8**, 3160–3165.
61. T. Sun, Z. J. Li, H. G. Wang, D. Bao, F. L. Meng and X. B. Zhang, *Angew. Chemie - Int. Ed.*, 2016, **55**, 10662–10666.
62. M. López-Herraiz, E. Castillo-Martínez, J. Carretero-González, J. Carrasco, T. Rojo and M. Armand, *Energy Environ. Sci.*, 2015, **8**, 3233–3241.
63. Y. Wu, Y. Chen, M. Tang, S. Zhu, C. Jiang, S. Zhuo and C. Wang, *Chem. Commun.*, 2019, **55**, 10856–10859.
64. G. S. Jeong, K. H. Jung, S. Choi and K. C. Kim, *ACS Sustain. Chem. Eng.*, 2020, **8**, 11328–11336.
65. C. Luo, J. J. Shea and J. Huang, *J. Power Sources*, 2020, **453**, 227904.
66. Q. Zhao, W. Zhao, C. Zhang, Y. Wu, Q. Yuan, A. K. Whittaker and X. S. Zhao, *Energy and Fuels*, 2020, **34**, 5099–5105.
67. M. S. Kim, M. Lee, M. J. Kim, Y. K. Jeong, J. K. Park and S. M. Paek, *J. Mater. Chem. A*, 2020, **8**, 17790–17799.
68. C. Wang, Y. Xu, Y. Fang, M. Zhou, L. Liang, S. Singh, H. Zhao, A. Schober and Y. Lei, *J. Am. Chem. Soc.*, 2015, **137**, 3124–3130.

69. S. Wu, W. Wang, M. Li, L. Cao, F. Lyu, M. Yang, Z. Wang, Y. Shi, B. Nan, S. Yu, Z. Sun, Y. Liu and Z. Lu, *Nat. Commun.*, 2016, **7**, 13318.
70. M. Lee, J. Hong, J. Lopez, Y. Sun, D. Feng, K. Lim, W. C. Chueh, M. F. Toney, Y. Cui and Z. Bao, *Nat. Energy*, 2017, **2**, 861–868.
71. M. Mao, C. Luo, T. P. Pollard, S. Hou, T. Gao, X. Fan, C. Cui, J. Yue, Y. Tong, G. Yang, T. Deng, M. Zhang, J. Ma, L. Suo, O. Borodin and C. Wang, *Angew. Chemie - Int. Ed.*, 2019, **58**, 17820–17826.
72. R. Shi, L. Liu, Y. Lu, C. Wang, Y. Li, L. Li, Z. Yan and J. Chen, *Nat. Commun.*, 2020, **11**, 178.
73. R. Thangavel, M. Moorthy, B. K. Ganesan, W. Lee, W. S. Yoon and Y. S. Lee, *Small*, 2020, **16**, 2003688.
74. W. Xiong, W. Huang, M. Zhang, P. Hu, H. Cui and Q. Zhang, *Chem. Mater.*, 2019, **31**, 8069–8075.
75. X. Wang, Z. Shang, A. Yang, Q. Zhang, F. Cheng, D. Jia and J. Chen, *Chem*, 2019, **5**, 364–375.
76. C. Luo, G. L. Xu, X. Ji, S. Hou, L. Chen, F. Wang, J. Jiang, Z. Chen, Y. Ren, K. Amine and C. Wang, *Angew. Chemie - Int. Ed.*, 2018, **57**, 2879–2883.
77. L. Y. Wang, C. Ma, X. Wei, B. Chang, K. X. Wang and J. S. Chen, *J. Mater. Chem. A*, 2020, **8**, 8469–8475.
78. S. Wang, L. Wang, Z. Zhu, Z. Hu, Q. Zhao and J. Chen, *Angew. Chemie*, 2014, **126**, 6002–6006.
79. S. Gu, S. Wu, L. Cao, M. Li, N. Qin, J. Zhu, Z. Wang, Y. Li, Z. Li, J. Chen and Z. Lu, *J. Am. Chem. Soc.*, 2019, **141**, 9623–9628.

80. K. Qin, J. Huang, K. Holguin and C. Luo, *Energy Environ. Sci.*, 2020, **13**, 3950–3992.
81. J. Huang, X. Dong, Z. Guo and Y. Wang, *Angew. Chemie - Int. Ed.*, 2020, **59**, 18322–18333.
82. C. Han, J. Zhu, C. Zhi and H. Li, *J. Mater. Chem. A*, 2020, **8**, 15479–15512.
83. Z. Tie and Z. Niu, *Angew. Chemie - Int. Ed.*, 2020, **59**, 21293–21303.
84. D. J. Kim, Y. H. Jung, K. K. Bharathi, S. H. Je, D. K. Kim, A. Coskun and J. W. Choi, *Adv. Energy Mater.*, 2014, **4**, 1400133.
85. D. Bin, F. Wang, A. G. Tamirat, L. Suo, Y. Wang, C. Wang and Y. Xia, *Adv. Energy Mater.*, 2018, **8**, 1703008.
86. Y. Liang, Y. Jing, S. Gheyhani, K. Y. Lee, P. Liu, A. Facchetti and Y. Yao, *Nat. Mater.*, 2017, **16**, 841–848.
87. H. Long, W. Zeng, H. Wang, M. Qian, Y. Liang and Z. Wang, *Adv. Sci.*, 2018, **5**, 1700634.
88. S. Perticarari, E. Grange, T. Doizy, Y. Pellegrin, E. Quarez, K. Oyaizu, A. J. Fernandez-Ropero, D. Guyomard, P. Poizot, F. Odobel and J. Gaubicher, *Chem. Mater.*, 2019, **31**, 1869–1880.
89. T. Gu, M. Zhou, M. Liu, K. Wang, S. Cheng and K. Jiang, *RSC Adv.*, 2016, **6**, 53319–53323.
90. H. Qin, Z. P. Song, H. Zhan and Y. H. Zhou, *J. Power Sources*, 2014, **249**, 367–372.
91. W. Deng, Y. Shen, J. Qian and H. Yang, *Chem. Commun.*, 2015, **51**, 5097–5099.
92. X. Dong, L. Chen, J. Liu, S. Haller, Y. Wang and Y. Xia, *Sci. Adv.*, 2016, **2**, e1501038.
93. T. Sun, C. Liu, J. Wang, Q. Nian, Y. Feng, Y. Zhang, Z. Tao and J. Chen, *Nano Res.*, 2020, **13**, 676–683.
94. S. Perticarari, Y. Sayed-Ahmad-Baraza, C. Ewels, P. Moreau, D. Guyomard, P. Poizot, F. Odobel and J. Gaubicher, *Adv. Energy Mater.*, 2018, **8**, 1701988.
95. L. Zhong, Y. Lu, H. Li, Z. Tao and J. Chen, *ACS Sustain. Chem. Eng.*, 2018, **6**, 7761–7768.

96. J. Heiska, M. Nisula and M. Karppinen, *J. Mater. Chem. A*, 2019, **7**, 18735–18758.
97. X. Zhu, R. Zhao, W. Deng, X. Ai, H. Yang and Y. Cao, *Electrochim. Acta*, 2015, **178**, 55–59.
98. X. Chi, Y. Liang, F. Hao, Y. Zhang, J. Whiteley, H. Dong, P. Hu, S. Lee and Y. Yao, *Angew. Chemie - Int. Ed.*, 2018, **57**, 2630–2634.
99. X. Chi, F. Hao, J. Zhang, X. Wu, Y. Zhang, S. Gheyhani, Z. Wen and Y. Yao, *Nano Energy*, 2019, **62**, 718–724.
100. F. Hao, X. Chi, Y. Liang, Y. Zhang, R. Xu, H. Guo, T. Terlier, H. Dong, K. Zhao, J. Lou and Y. Yao, *Joule*, 2019, **3**, 1349–1359.
101. K. S. Weeraratne, A. A. Alzharani and H. M. El-Kaderi, *ACS Appl. Mater. Interfaces*, 2019, **11**, 23520–23526.
102. L. Zhu, J. Liu, Z. Liu, L. Xie and X. Cao, *ChemElectroChem*, 2019, **6**, 787–792.
103. Y. Zhang, H. Guo, W. Li, Y. Huang, Z. Zhang, G. Liu and Y. Wang, *ChemSusChem*, 2019, **12**, 4160–4164.
104. J. M. Cabañero, V. Pimenta, K. C. Cannon, R. E. Morris and A. R. Armstrong, *ChemSusChem*, 2019, **12**, 4522–4528.
105. A. Tripathi, Y. Chen, H. Padhy, S. Manzhos and P. Balaya, *Energy Technol.*, 2019, **7**, 1801030.
106. H. Lyu, C. J. Jafta, I. Popovs, H. M. Meyer, J. A. Hachtel, J. Huang, B. G. Sumpter, S. Dai and X. G. Sun, *J. Mater. Chem. A*, 2019, **7**, 17888–17895.
107. J. Li, M. Luo, Z. Ba, Z. Wang, L. Chen, Y. Li, M. Li, H. B. Li, J. Dong, X. Zhao and Q. Zhang, *J. Mater. Chem. A*, 2019, **7**, 19112–19119.
108. M. Ruby Raj, R. V. Mangalaraja, D. Contreras, K. Varaprasad, M. V. Reddy and S. Adams, *ACS Appl. Energy Mater.*, 2020, **3**, 240–252.

109. Y. Hu, Y. Gao, L. Fan, Y. Zhang, B. Wang, Z. Qin, J. Zhou and B. Lu, *Adv. Energy Mater.*, 2020, **10**, 2002780.
110. S. Eder, D. J. Yoo, W. Nogala, M. Pletzer, A. Santana Bonilla, A. J. P. White, K. E. Jelfs, M. Heeney, J. W. Choi and F. Glöcklhofer, *Angew. Chemie - Int. Ed.*, 2020, **59**, 12958–12964.
111. Y. Wu, X. Chen, G. Lin, X. Zhu, J. Qiu, Y. Luo, Z. Xu, Q. Chen, V. Ganesh and R. Zeng, *J. Electroanal. Chem.*, 2020, **877**, 114749.
112. L. Yang, P. Wang, S. Zhang, Y. Wang, L. Zang, H. Zhu, J. Yin and H. Y. Yang, *J. Mater. Chem. A*, 2020, **8**, 22791–22801.
113. X. Gao, Y. Chen, C. Gu, J. Wen, X. Peng, J. Liu, Z. Zhang, Q. Zhang, Z. Liu and C. Wang, *J. Mater. Chem. A*, 2020, **8**, 19283–19289.
114. S. W. Zhang, T. Cao, W. Lv, J. Zhang, Y. Tao, F. Kang, D. W. Wang and Q. H. Yang, *Nano Energy*, 2020, **77**, 105203.
115. C. Wang, R. Chu, Z. Guan, Z. Ullah, H. Song, Y. Zhang, C. Yu, L. Zhao, Q. Li and L. Liu, *Nanoscale*, 2020, **12**, 4729–4735.
116. T. Yang, C. Zhang, W. Ma, X. Gao, C. Yan, F. Wang and J. X. Jiang, *Solid State Ionics*, 2020, **347**, 115247.
117. C. Cui, X. Ji, P. F. Wang, G. L. Xu, L. Chen, J. Chen, H. Kim, Y. Ren, F. Chen, C. Yang, X. Fan, C. Luo, K. Amine and C. Wang, *ACS Energy Lett.*, 2020, **5**, 224–231.
118. Y. Kim, W. Wu, S., Chun, J. F. Whitacre, and C. J. Bettinger, *PNAS*, 2013, 110, **52**, 20912–20917 .
119. N. Chikushi, H. Yamada, K. Oyaizu, and H. Nishide, *Sci. China Chem.*, 2012, **55**, 822–829.
120. S. Renault, V. A. Mihali, K. Edström, D. Brandell, *Electrochem. Commun.*, 2014, **45**, 52–55.

121. A. Li, Z. Feng, Y. Sun, L. Shang, L. Xu, *J. Power Sources*, 2017, **343**, 424-430.
122. M. Tang, S. Zhu, Z. Liu, C. Jiang, Y. Wu, H. Li, B. Wang, E. Wang, J. Ma, C. Wang, *Chem*, 2018, **4**, (11), 2600-2614.
123. S. Yang, Y. Chen, G. Zhou, and Z. Fu, *J. Electrochem. Soc.*, 2018, **165**, (7) A1422-A1429.
124. H. Li, M. Tang, Y. Wu, Y. Chen, S. Zhu, B. Wang, C. Jiang, E. Wang, and C. Wang, *J. Phys. Chem. Lett.*, 2018, **9**, 3205-3211.
125. H. Zhang, W. Sun, X. Chen, and Y. Wang, *ACS Nano*, 2019, **13**, 14252-14261.
126. H. Duan, P. Lyu, J. Liu, Y. Zhao, and Y. Xu, *ACS Nano*, 2019, **13**, 2473-2480.
127. Q. Yang, Y. Wang, R. Zhao, D. He, Y. Fang, W. Xue, and X. Ma, *J. Electrochem. Soc.*, 2019, **166**, (2), A201-A207.
128. F. A. Obrezkov, A. F. Shestakov, V. F. Traven, K. J. Stevenson, and P. A. Troshin, *J. Mater. Chem. A*, 2020, **7**, 11430.
129. Y. Chen, H. Li, M. Tang, S. Zhuo, Y. Wu, E. Wang, S. Wang, C. Wang, and W. Hu, *J. Mater. Chem. A*, 2019, **7**, 20891.
130. M. Kato, T. Masese, M. Yao, N. Takeichi, and T. Kiyobayashi, *New J. Chem.*, 2019, **43**, 1626.
131. W. Tang, H. He, J. Shi, B. Cao, C. Yang, C. Fan, *Org. Electron.*, 2019, **75**, 105386.
132. D. Li, W. Tang, C. Y. Yong, Z. H. Tan, C. Wang, and C. Fan, *Chem. Sus. Chem.*, 2020, **13**, 1991-1996.
133. M. Zhou, Y. Xiong, Y. Cao, X. Ai, H. Yang, *J. Polym. Sci. B Polym. Phys.*, 2012, **51**, 114-118.
134. W. Deng, X. Liang, X. Wu, J. Qian, Y. Cao, X. Ai, J. Feng, and H. Yang, *Sci. Rep.*, 2013, **3**, 2671.

135. L. Zhu, Y. Shen, M. Sun, J. Qian, Y. Cao, X. Ai, and H. Yang, *Chem. Commun.*, 2013, **49**, 11370.
136. S. C. Han, E. G. Bae, H. Lim, M. Pyo, *J. Power Sources*, 2014, **254**, 73-79.
137. H. Wang, S. Yuan, D. Ma, X. Huang, F. Meng, and X. Zhang, *Adv. Energy Mater.*, 2014, **4**, 1301651.
138. W. Luo, M. Allen, V. Raju, and X. Ji, *Adv. Energy Mater.*, 2014, **4**, 1400554.
139. Z. Zhu, H. Li, J. Liang, Z. Tao, and J. Chen, *Chem. Commun.*, 2015, **51**, 1446.
140. Z. Li, J. Zhou, R. Xu, S. Liu, Y. Wang, P. Li, W. Wu, M. Wu, *Chem. Eng. J.*, 2016, **287**, 516-522.
141. J. Hu, R. Liang, W. Tang, H. He, C. Fan, *Int. J. Hydrogen Energ.*, 2020, **45**, 24573-24581
142. S. Xu, H. Li, Y. Chen, Y. Wu, C. Jiang, E. Wang, and C. Wang, *J. Mater. Chem. A*, 2020, **8**, 23851.
143. M. R. Raj, N. Kim, and G. Lee, *Sustainable Energy Fuels*, 2021, **5**, 175.
144. K. Qin, K. Holguin, M. Mohammadiroudbari and C. Luo, *Chem. Commun.*, 2021, DOI: 10.1039/d0cc08273b.
145. C. Ma, X. Zhao, L. Kang, K. X. Wang, J. S. Chen, W. Zhang and J. Liu, *Angew. Chemie - Int. Ed.*, 2018, **57**, 8865–8870.