


 Cite this: *Nanoscale*, 2022, **14**, 13551

Competition between reverse water gas shift reaction and methanol synthesis from CO₂: influence of copper particle size†

 Laura Barberis, ^a Amir H. Hakimioun,^b Philipp N. Plessow, ^b Nienke L. Visser,^a Joseph A. Stewart, ^c Bart D. Vandegehuchte,^c Felix Studt ^{b,d} and Petra E. de Jongh *^a

Converting CO₂ into value-added chemicals and fuels, such as methanol, is a promising approach to limit the environmental impact of human activities. Conventional methanol synthesis catalysts have shown limited efficiency and poor stability in a CO₂/H₂ mixture. To design improved catalysts, crucial for the effective utilization of CO₂, an in-depth understanding of the active sites and reaction mechanism is desired. The catalytic performance of a series of carbon-supported Cu catalysts, with Cu particle sizes in the range of 5 to 20 nm, was evaluated under industrially relevant temperature and pressure, *i.e.* 260 °C and 40 bar(g). The CO₂ hydrogenation reaction exhibited clear particle size effects up to 13 nm particles, with small nanoparticles having the lower activity, but higher methanol selectivity. MeOH and CO formation showed a different size-dependence. The TOF_{CO} increased from 1.9 × 10⁻³ s⁻¹ to 9.4 × 10⁻³ s⁻¹ with Cu size increasing from 5 nm to 20 nm, while the TOF_{MeOH} was size-independent (8.4 × 10⁻⁴ s⁻¹ on average). The apparent activation energies for MeOH and CO formation were size-independent with values of 63 ± 7 kJ mol⁻¹ and 118 ± 6 kJ mol⁻¹, respectively. Hence the size dependence was ascribed to a decrease in the fraction of active sites suitable for CO formation with decreasing particle size. Theoretical models and DFT calculations showed that the origin of the particle size effect is most likely related to the differences in formate coverage for different Cu facets whose abundance depends on particle size. Hence, the CO₂ hydrogenation reaction is intrinsically sensitive to the Cu particle size.

 Received 11th May 2022,
 Accepted 2nd August 2022
 DOI: 10.1039/d2nr02612k

rsc.li/nanoscale

Introduction

Global warming is considered one of the most serious environmental problems in recent years. The greenhouse gas contributing the most from human activities is carbon dioxide (CO₂).¹ A promising approach is the conversion of CO₂ into value-added bulk chemicals and fuels, such as oxygenates (alcohols and dimethyl ether) and hydrocarbons (olefins, liquid hydrocarbons, and aromatics). Methanol is a common chemical feedstock in industry and potentially a substitute for fossil fuels.² Global methanol demand reached 98.3 Mt in

2019, and is expected to surpass 120 Mt by 2025.³ Currently, methanol is almost exclusively produced from either natural gas or coal, mostly due to economic reasons. The industrial process involves the hydrogenation of CO₂-enriched syngas over Cu/ZnO/Al₂O₃ catalysts at 240–260 °C and 40–100 bar.^{4,5}

It is generally accepted that the main carbon source in the process is CO₂, which is generated by the water–gas shift reaction (CO + H₂O → CO₂ + H₂) and converted into methanol (CO₂ + 3H₂ → CH₃OH + H₂O).⁶ The WGS reaction is beneficial for the catalyst's stability as it consumes the water generated during methanol synthesis. When CO₂ is the only carbon source in the feedstock, besides being hydrogenated to methanol, CO₂ is also consumed by the reverse water gas shift reaction (CO₂ + H₂ → CO + H₂O). The undesired competitive rWGS reaction has to be avoided to optimize the MeOH selectivity. Moreover, the extra water formed as by-product by rWGS reaction could cause rapid catalyst degradation. These two factors make pure CO₂ hydrogenation more challenging than conventional methanol synthesis.⁷ Another, challenge is the high thermodynamic stability of CO₂, which means that a very good catalyst to operate at low temperatures is needed.⁸

^aMaterials Chemistry and Catalysis, Debye Institute for Nanomaterials Science, Utrecht University, Universiteitsweg 99, 3584 CG Utrecht, The Netherlands.
 E-mail: P.E.deJongh@uu.nl

^bInstitute of Catalysis Research and Technology, Karlsruhe Institute of Technology, Eggenstein-Leopoldshafen 76344, Germany

^cTotalEnergies OneTech Belgium, B-7181 Seneffe, Belgium

^dInstitute for Chemical Technology and Polymer Chemistry, Karlsruhe Institute of Technology, Karlsruhe 76131, Germany

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2nr02612k>



generation catalysts often show, during the first hours in a reaction gas feed, slight changes in the catalytic performance mainly due to nanoparticle restructuring.^{15,53,55} Hence an activation procedure was performed. This procedure consisted of exposing the catalysts to the reaction conditions (260 °C, 40 bar(g) pressure of CO₂/H₂/He gas mixture) for 20 hours. After the activation procedure, performed in the catalytic setup, the samples were slowly passivated by air exposure at room temperature and subsequently analysed by transmission electron microscopy (TEM) and powder X-ray diffraction (XRD). The catalysts were named X₂Cu/C, in which X represents the surface-averaged CuO size in the activated catalyst measured by TEM.

Catalyst characterization

Surface area (S_{BET}) and total pore volume (V_p) of the pristine supports were determined from N₂ physisorption measurements at -196 °C in a TriStar Plus II gas-volumetric apparatus (Micromeritics), using Carbon Black STSA as a reference. The specific surface area of the support was calculated by fitting with a Brunauer–Emmett–Teller isotherm,⁵⁶ whereas the total pore volume was derived from the absorbed volume of nitrogen at $p/p_0 = 0.95$.

X-ray diffraction (XRD) was performed on a Bruker AXS D8 Advance diffractometer using Co ($K_{\alpha} = 1.79026 \text{ \AA}$) radiation. Patterns were collected from 20° to 70° 2θ . Diffractograms were measured in inert Ar atmosphere (silicon wafers with an X-ray transparent airtight dome) for the reduced catalysts and in air for the passivated and activated catalysts. All diffractograms were normalized to the intensity of the graphitic carbon (002) diffraction peak at 30.9° 2θ . The crystallite sizes were calculated by applying the Scherrer equation to the Cu⁰ (200) diffraction at 59.3 degrees.⁵⁷

Transmission electron microscopy (TEM) was performed either on a Tecnai 20 (FEI) or on a Talos F200X (FEI), both operated at 200 kV. TEM samples were prepared by directly applying the pre-ground sample powder to copper carbon-coated TEM grids (Agar, 300 mesh). TEM imaging was performed on the passivated catalysts, the activated catalysts and the used catalysts. The size of >400 nanoparticles was determined using ImageJ software. All particle sizes are reported as

surface-averaged particle size $d_s = \frac{\sum_{i=1}^N d_i^3}{\sum_{i=1}^N d_i^2}$ with the corresponding

standard error in the particle size $\sigma_{ds} = \sqrt{\frac{\sum_{i=1}^N (d_i - d_n)^2}{N}}$.

Catalyst performance

The performance of the catalysts was investigated in a gas-phase fixed-bed 16 parallel reactor system (Flowrence, Avantium). Each stainless steel plug flow reactor of 2.6 mm

inner diameter was loaded with 4.2 mg of Cu mass on carbon (sieve fraction 75–150 μm) diluted with SiC (212–425 μm), with an inert fraction between 0.6 and 0.9. Prior to reaction, the catalysts were reduced *in situ* in 10 vol% H₂/N₂ flow at 10.9 mL min⁻¹ 200 °C for 3.5 hours with 2 °C min⁻¹ under atmospheric pressure. Afterwards, the temperature was lowered to 120 °C and the atmosphere was switched to H₂/CO₂/He = 67.5/22.5/10 vol% and the reactor was pressurized. Two separate runs were performed to evaluate the long-term stability of the catalysts and the catalytic performances at different temperatures.

For the isothermal stability test, after introduction of the H₂/CO₂/He = 67.5/22.5/10 vol% mixture, the temperature was set to 260 °C and the pressure to 40 bar(g). These conditions were kept constant for over 140 hours. During the performance evaluation test, first a 23 hours stabilizing protocol was performed to ensure the steady state operation and minimize the influence of activation/deactivation behavior. The stabilizing protocol was performed at 260 °C temperature and 40 bar(g) pressure under H₂/CO₂/He = 67.5/22.5/10 vol% at 2.5 mL min⁻¹ atmosphere. The catalysts characterized after undergoing the stabilizing protocol will be referred to as ‘activated catalysts’. Subsequently, without changes in the gas flow, the reactor temperature was lowered to 200 °C and the temperature was then varied between 200 and 260 °C, with isothermal segments of 20 hours for each temperature.

Reactants and products of the reactions were analyzed online with an Aligent 7890B gas chromatograph at 14 min intervals. Permanent gasses were separated on a HayeSep Q column (0.5 m × 1/8 inch ID) and MolSieve 5A column (2.4 m × 1/8 inch ID) and analysed using a thermal conductivity detector. Hydrocarbons and oxygenates were analysed using two separate flame ionization detectors, in combination with a GS-GasPro column (30 m × 0.32 mm ID) and a HP-Innowax column (30 m × 0.32 mm ID). Details on the calculations of activity and selectivity are given in section S2.†

DFT calculations

DFT calculations were carried out using the Vienna Ab Initio Simulation Package (VASP)^{58,59} and the Atomic Simulation Environment (ASE)⁶⁰ employing the Bayesian error estimation functional with van der Waals corrections (BEEF-vdW)^{61,62} and the projector-augmented wave (PAW) potentials.⁶³ We chose the BEEF-vdW functional as it has a reasonable performance regarding adsorption energies on transition-metal surfaces.⁶⁴ Importantly, this functional has also been shown to successfully describe processes on copper surfaces relevant for the CO₂ hydrogenation to methanol.⁶⁵ The lattice constant of bulk copper was optimized to 3.664 Å using an energy cutoff of 800 eV and a 16 × 16 × 16 Monkhorst–Pack⁶⁶ k -point sampling. The kinetic energy cutoff for all slab calculations was 450 eV. The surfaces were modelled by 4 layer supercells separated by 18 Å in the z -direction. The different sizes and corresponding k -point sampling used to calculate the various coverages are given in Table S4.† In all calculations the bottom two layers were kept fixed at the bulk position while the top two layers



and the adsorbate were allowed to relax until atomic forces were smaller than $0.01 \text{ eV } \text{\AA}^{-1}$. Adsorption energies were calculated relative to the corresponding gas-phase species (CO_2 and $\frac{1}{2} \text{H}_2$ in the case of formate and carboxyl). The correction of the well-known gas-phase errors for CO_2 (+0.41 eV) and H_2 (+0.09 eV) has been taken from the literature.³⁹ Using this correction we obtain an adsorption enthalpy of formate on Cu(100) of 84–91 kJ mol^{-1} for coverages of 0.12 to 0.5 ML. This compares with 80–100 kJ mol^{-1} reported for measurements on Cu(100) single crystal surfaces.⁶⁷ Zero-point energy (ZPE) and entropic contributions were taken from the literature as obtained for the Cu(211) surface calculated with the BEEF-vdW functional³⁹ and are listed in Table S5† and the total energies of all systems reported here in Table S6.†

Results and discussion

Catalyst stability and structural properties

Carbon was selected as support material to avoid strong metal–support interactions while studying the relationship between the catalytic performance during CO_2 hydrogenation and Cu particle size. However, the use of a support with a relatively weak interaction can result in a rapid loss of accessible metal surface area due to particle growth.⁵⁵ Hence, we first evaluated the stability of the Cu/C catalysts under isothermal reaction conditions, *i.e.* at 40 bar(g) and 260 °C for over 140 hours on stream. A typical reaction profile of CO_2 conversion and selectivity towards methanol is shown in Fig. 1. After an initial decrease in the first 20–40 hours, the CO_2 conversion remained stable around 10%. Under these experimental conditions, equilibrium corresponds to 22% CO_2 conversion. MeOH and CO were the two main products detected. MeOH and CO selectivity remained stable around 19% and 81% respectively under these conditions.



Fig. 1 CO_2 conversion and methanol selectivity as a function of time on stream (TOS) for the 4.7_Cu/C catalyst with 5.2 wt% Cu. Reaction conditions: 4.2 mg of Cu per reactor, 40 bar(g), 260 °C, $600 \text{ mL min}^{-1} \text{g}_{\text{Cu}}^{-1}$, $\text{H}_2/\text{CO}_2/\text{He} = 67.5/22.5/10 \text{ vol}\%$.

Particle growth during catalysis was evaluated by comparing the Cu particle size before and after catalysis and the surface-normalized turn-over frequencies at the beginning of the catalytic test and after 140 hours on stream. The 4.7_Cu/C catalyst showed an increase in Cu particle size from $3.9 \pm 0.9 \text{ nm}$ to $4.9 \pm 1.2 \text{ nm}$. The complete collection of transmission electron micrographs and particle size distributions of the as-synthesized and used catalysts is depicted in Fig. S1 and Table S1.† The TOF was $3.1 \times 10^{-3} \text{ s}^{-1}$ after 8 hours on stream considering the initial Cu particle size, and $2.4 \times 10^{-3} \text{ s}^{-1}$ after 140 hours on stream considering the final Cu particle size. Hence particle growth was limited, and the loss of active surface area seemed to be the main cause of activity loss.

The most representative image of the catalysts under reaction conditions, considering the initial changes in activity and selectivity during catalysis, is represented by the catalysts after exposure to reaction conditions (260 °C, 40 bar(g) pressure of $\text{CO}_2/\text{H}_2/\text{He}$ gas mixture) for 20 hours, the so-called activation procedure. Table 1 shows the structural properties of a series of Cu on carbon catalysts that underwent the activation procedure, showing different particle sizes. Fig. 2 (frame a and b) shows transmission electron micrographs and particle size distributions for two representative Cu/C catalysts. The complete collection of micrographs is depicted in Fig. S1,† and properties reported in Table S1.†

TEM analysis showed highly dispersed copper nanoparticle (black dots) on the graphitic carbon sheets for all the catalysts. The diffractograms of the activated catalysts are shown in Fig. 2 (frame c), while the diffractograms of the as-synthesized and used catalysts are shown in Fig. S2.† Next to the graphitic carbon diffraction peaks, diffraction lines are present that can be attributed to CuO, Cu_2O and metallic Cu. As expected from the short exposure to air of the samples after activation, different phases of copper oxide were present. The 19.4_Cu/C catalyst exhibited the most intense diffraction peaks of Cu^0 (111) and (200) as well as of Cu^{2+} (002), in accordance with the highest Cu weight loading. TEM and XRD analysis prove that catalysts with particle sizes in the range of 4.7 to 19.4 nm were obtained after activation. By comparing the structural properties and particle sizes of the as-synthesized catalysts, as

Table 1 Structural properties of the carbon-supported Cu catalysts

Name	Cu loading (wt%)	$d_s \pm \sigma_{ds}^a$ (nm)	Cu^0 crystallite size ^b (nm)	Cu dispersion ^c (%)
4.7_Cu/C	5.2	4.7 ± 1.2	—	22.1
5.8_Cu/C	9.9	5.8 ± 1.6	—	17.9
11.2_Cu/C	9.9	11.2 ± 3.6	7.5	9.3
12.8_Cu/C	9.9	12.8 ± 4.1	9.6	8.1
19.4_Cu/C	14.1	19.4 ± 6.4	12.4	5.4

^a TEM-derived surface-averaged particle size and relative size distribution. ^b Cu^0 crystallite size as determined by XRD using the Cu^0 (200) diffraction peak of the activated catalysts. ^c The Cu dispersion (fraction of surface Cu atoms at the surface) calculated using the TEM-determined mean diameter (d_s) of the activated catalyst. More detail are given in the ESI (section S2†).





Fig. 2 Transmission electron micrographs with corresponding particle size distributions of the 4.7_Cu/C (a) and 19.4_Cu/C (b) catalysts after activation. (c) Powder X-ray diffractograms of the activated Cu/C catalysts, diffractograms normalized to the intensity of the carbon (002) diffraction peak and vertically offset for clarity.

reported in Table S1[†] it is evidenced that the diversity and broad range of sizes, from 3.9 to 18.0 nm in the fresh catalysts, was preserved during the activation procedure. By comparison of the particle sizes of the activated and used catalysts, it is noted that average particle sizes do not vary significantly beyond the activation procedure (Table S1[†]). The average particle sizes, as determined by TEM, of the 4.7_Cu/C and 19.4_Cu/C catalysts after activation are 4.7 and 19.4 nm, while after 120 hours on stream are, respectively, 4.9 and 21.2 nm. This highlights the importance of the activation procedure to obtain structurally stable catalysts in order to study the influence of the copper particle size during CO₂ hydrogenation reaction.

Copper particle size effect on CO₂ conversion

The performance of the Cu catalysts in CO₂ hydrogenation, with copper particle sizes ranging from 4.7 to 19.4 nm (referred to the activated state), was investigated under a 3 : 1 ratio of H₂/CO₂ mixture at 40 bar(g) in the temperature range between 200 and 260 °C. Fig. 3 reports the CO₂ conversion and weight-normalized copper time yield (CTY) for selected Cu/C catalysts. A limited loss of activity is observed at 260 °C during the first 20 hours of catalysis, as reported above. After the first



Fig. 3 Characteristic profiles for CO₂ conversion and weight-normalized copper time yield for Cu/C catalysts as function of TOS (h) at different temperatures. Reaction conditions: 4.2 mg of Cu per reactor, 40 bar(g), 600 mL min⁻¹ g_{Cu}⁻¹, H₂/CO₂/He = 67.5/22.5/10 vol%.

20 hours, the conversion is stable at all the temperatures tested.

The relationship between TOF and surface-averaged Cu particle size after use is shown in Fig. 4. Approximately a 3-fold increase in TOF was observed with increasing surface-averaged Cu particle size from 5 to 13 nm (at 260 °C the TOF increased from 2.6×10^{-3} s⁻¹ to 7.5×10^{-3} s⁻¹), while no further increase was observed for particles larger than 13 nm. These results confirm that the CO₂ hydrogenation reaction is sensitive to the Cu particle size. A similar trend was observed at lower temperatures (Fig. S3[†]). At 260 °C the CO₂ conversions were relatively high (7–15%), but still well below the equilibrium conversion (22%); see Fig. S4[†] for a graphical comparison.

A similar copper particle size effect has been observed for methanol synthesis from CO₂ enriched syngas⁶⁸ as well as for



Fig. 4 TOF and pre-exponential factor as a function of Cu particle size. Line is drawn to guide the eye. Reaction conditions: 4.2 mg of Cu per reactor, 40 bar(g), 260 °C, 600 mL min⁻¹ g_{Cu}⁻¹, H₂/CO₂/He = 67.5/22.5/10 vol%.



ethyl acetate hydrogenation,²⁵ while for CO₂ hydrogenation to methanol divergent results have been reported. Arena *et al.*³¹ reported that the TOF of Cu-Zn/ZrO₂ catalysts increased linearly with increasing Cu particle size in the range between 2 and 32 nm. On the other hand, Natesakhawat *et al.*³² showed an opposite trend for Cu catalysts containing Zr/Zn/Ga/Y in different combinations. In both studies, the presence of promoters and the use of oxidic supports might have obscured the intrinsic relationship between the Cu particle size and catalytic performance. An overview of CO₂ TOF values observed in this study and values reported in literature is reported in Fig. S5 and Table S2.† CO₂ TOF values reported in this study are of the same order of magnitude as those previously reported. However, this is the first time that the effect of the copper particle size supported on rather inert carbon support has been studied at industrially relevant conditions (40 bar(g) pressure and 200–260 °C).

Different phenomena can lead to particle size effects such as size-dependent interactions with the support, electronic particle size effects and structure sensitivity of the reaction itself.^{69,70} The chemically inert nature of the carbon support makes a strong influence of the support unlikely.^{71–73} In the size range studied (larger than 3 nm), electronic particle size effects are not expected to play a significant role.^{69,74,75} The particle size effect observed in these systems is hence likely due to structure sensitivity, which is related to the size dependence of the fraction of different types of copper surface sites.

The apparent activation energies were calculated using the Arrhenius model (Fig. S6† frame a). The obtained energy values for CO₂ hydrogenation (Table S3 and Fig. S6† frame b) were, within the error, size-independent with an average E_a of 74 ± 7 kJ mol⁻¹. The pre-exponential factor (A) was calculated using the surface-normalized CTY and an averaged E_a of 74 kJ mol⁻¹. The pre-exponential factor increased from 3.7×10^6 for 4.7 nm particles to 1×10^7 for 12.8 nm and did

not increase further for larger nanoparticles. This suggests the presence of well-defined and size-independent active Cu sites responsible for CO₂ conversion, for which the relative abundance increases with increasing particle size up to around 13 nm.

Influence of copper particle size on product selectivity

So far we have only considered the effect of copper particle size on the overall conversion of CO₂ without considering the products formed. Methanol and carbon monoxide were the main products for all catalysts at all temperatures tested (200–260 °C). Additionally, traces of CH₄ (less than 0.6% selectivity) were observed at temperatures above 220 °C, which might be due to minor contamination.²⁴ Fig. 5 (frame a) shows the methanol selectivity for different Cu particle sizes as a function of CO₂ conversion. Different CO₂ conversions were obtained by varying the temperature in the range of 200–260 °C. For all particle sizes, the MeOH selectivity decreased as the conversion increased.

When comparing at constant conversion (Fig. 5 frame b), the influence of particle size on selectivity is even more clear. Small nanoparticles display a greatly enhanced selectivity towards MeOH over CO as a product. For example, at 5% CO₂ conversion 4.7_Cu/C shows a MeOH selectivity of 34%, whereas 19.4_Cu/C presents a MeOH selectivity of around 15% only. This influence of the particle size on product selectivity cannot be explained by the impact of conversion effect; it is clearly an intrinsic particle size effect.

To better understand the origin of the observed particle size effect, we considered separately the methanol and carbon monoxide formation rates. MeOH and CO turn-over-frequencies (respectively TOF_{MeOH} and TOF_{CO}) are displayed in Fig. 6. The TOF_{CO} at 260 °C clearly increased from 1.9×10^{-3} s⁻¹ to 9.4×10^{-3} s⁻¹ when the Cu size increased from 5 nm to 20 nm. The data on the formation rate of MeOH suggest a size-independent TOF_{MeOH} of 8.4×10^{-4} s⁻¹ on average, perhaps with



Fig. 5 (a) MeOH selectivity as a function of CO₂ conversion for catalysts with different Cu particle sizes. (b) Selectivity to MeOH as a function of Cu particle size for a CO₂ conversion of ~5%. The trend line was added to guide the eye. Reaction conditions: 4.2 mg of Cu per reactor, 40 bar(g), 600 mL min⁻¹ g_{Cu}⁻¹, H₂/CO₂/He = 67.5/22.5/10 vol%.





Fig. 6 MeOH and CO TOF as a function of the Cu particle size. Trend lines were added to guide the eye. Reaction conditions: 4.2 mg of Cu per reactor, 40 bar(g), 260 °C, 600 mL min^{-1} $\text{g}_{\text{Cu}}^{-1}$, $\text{H}_2/\text{CO}_2/\text{He} = 67.5/22.5/10$ vol%.

the exception of the smallest particles that apparently have a lower TOF_{MeOH} . Consequently, as the CO formation is much less favourable on smaller Cu clusters, they show the highest methanol selectivity.

The apparent activation energies for MeOH as well as for CO formation calculated using the Arrhenius model (Fig. S7†) are reported in Table S3.† The apparent activation energies for MeOH formation ranged from 55 to 76 kJ mol^{-1} , with data suggesting a slight increase for larger particle sizes. In literature, apparent activation energies for methanol formation of 73–100 kJ mol^{-1} have been reported for Cu– SiO_2 catalysts and of 77 kJ mol^{-1} for polycrystalline Cu foil.^{29,45} Carbon monoxide formation apparent activation energies ranged from 108 to 126 kJ mol^{-1} , with no significant dependence on particle size, while reported literature E_a values for Cu/ SiO_2 and polycrystalline Cu foil were 100–118 kJ mol^{-1} and 135 kJ mol^{-1} respectively.^{29,45} Therefore, the values obtained in this work are in line with the previously reported values for similar copper-based catalysts. The high MeOH selectivity of the smallest particles is here probably due to a lower fraction of sites that favour CO formation.

The origin of the particle size effect

MeOH and CO formation show two distinctly different and size-independent activation energies suggesting that the nature of the sites where MeOH and CO are formed is the same regardless of the size of the nanoparticles. Moreover, a higher value of apparent activation energy for CO (118 \pm 6 kJ mol^{-1}) than MeOH (63 \pm 7 kJ mol^{-1}) indicates that MeOH is unlikely to be formed *via* CO intermediates. TOF_{CO} and TOF_{MeOH} show different particle size-dependence. In particular, CO TOF increases with an increase in particle size, since this dependence cannot be correlated to changes in the

nature of the active site, which indicates that the abundance of active sites for rWGS reaction increase with an increase in particle size. In order to understand the particle size effect in terms of surface sites that are likely to be more active for MeOH synthesis and which for CO formation, we calculated the theoretical fraction of different surface sites and the corresponding adsorption free energies for reaction intermediates by DFT calculation.

We note that the smallest particles considered in this work are in the range of 3.9 ± 0.9 nm, which is above the limit above where electronic particle size effects have been shown to disappear for copper nanoparticles. This was evident from calculated adsorption energies of atomic oxygen, an important descriptor for CO_2 hydrogenation, which reached the bulk limit from 2.5 nm particles onwards.⁷⁶ We, therefore, turned our attention to another factor that is dependent on the particle size: the ratio of various surface terminations. Thus, we considered how the concentration of these surface sites varies with particle size. This is shown in Fig. 7 (frame a) where the fraction of surface atoms exhibiting a specific generalized coordination number (GCN)⁷⁷ is given as a function of particle size assuming ideal cuboctahedral copper particles. We stress that this analysis assumes ideal particle shapes and that our aim is to deduct qualitative trends rather than quantitative numbers. Fig. 7 (frame a) shows that the number of edge sites with a GCN of 5.33 decreases from around 20% to less than 5% when going from 3 to 30 nm. On the other hand the fraction of the more close packed (111) and (100) facets increases from 3 and 10% to more than 30 and 50%, respectively. The decrease in rWGS rate with decreasing size seems related to a decrease in concentration of terrace sites (*e.g.* (100) surfaces).

Both, CO_2 hydrogenation to methanol and the rWGS have been shown to be structure sensitive on copper surfaces.^{19,29,36,38} For methanol synthesis, it has been shown that sites with a low coordination number are more active, *e.g.* when comparing single crystal measurements on Cu(100) with those on Cu(110).^{19,29,35,36,78} Surface defects, as *e.g.* modeled by Cu(211) surfaces have indeed been suggested as active sites for copper-based catalysts.¹⁹ Likewise, the rWGS has also been shown to exhibit lower barriers on more undercoordinated surfaces, although kinetic modeling indicates that this does not necessarily translate to higher reaction rates.^{29,36,48,79,80} An interesting difference between methanol and CO formation is that the former is assumed to proceed *via* the formate intermediate, while CO formation occurs either *via* the carboxyl intermediate or through direct splitting of CO_2 .^{27,38,46,47,81,82} The higher apparent activation energy for CO than MeOH formation suggests that it is implausible that CO is a main intermediate in the MeOH synthesis. Given that formate is the only intermediate that is found to have significant surface coverages, we calculated the adsorption free energy of formate on a range of different copper surfaces for coverages of up to 1 mono layer (ML) using density functional theory (DFT) (see Fig. 7 frame b). The GCN for our models of edges ((211) and (110) surfaces) and corner atoms ((321) surface) differ slightly from that of the cuboctahedral particle, but they are close



a) Distribution of surface atoms for cuboctahedral particles

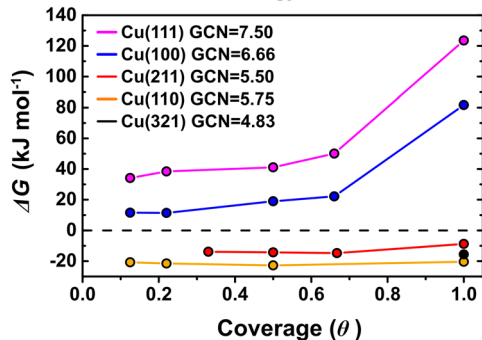
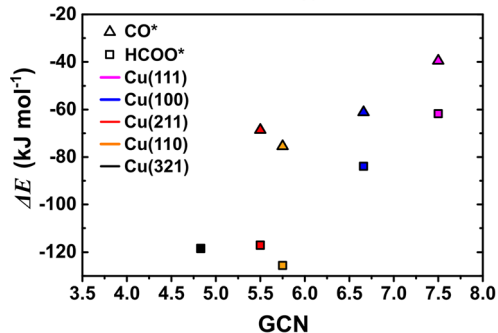
b) Formation free energy of formate HCOO^* c) Adsorption energy at $\theta = 0.5$ 

Fig. 7 (a) Fraction of surface atoms with a specific GCN as a function of particle diameter for cuboctahedral particles. GCN for the various surface atoms of a Cu_{1415} particle are shown in the inset. (b) Adsorption free energy of formate as a function of coverage for Cu(111) (pink), Cu(100) (blue), Cu(211) (red), Cu(110) (orange) and Cu(321) (black) surfaces at 500 K and 1 bar of H_2 and CO_2 . The coverage is normalized to 1 ML for one formate per two copper atoms of the corresponding facet (see section S3† for structures). (c) Adsorption energy of formate (squares) and CO (triangles) as a function of GCN.

enough to be used as a rough guidance. Our calculations reveal that the adsorption free energies decrease in the order $\text{Cu}(321) \approx \text{Cu}(110) > \text{Cu}(211) \gg \text{Cu}(100) \gg \text{Cu}(111)$. Interestingly, the effect of coverage (here 1 ML is defined as one formate per two copper surface atoms, see section S3† for details) is small for the (211) and (110) surfaces but has a sig-

nificant influence on the binding energy on Cu(111) and Cu(100). Importantly, at 500 K the adsorption free energy of formate on the (211) and (110) surfaces is negative, but positive on (111) and (100). This indicates that both (211) and (110) are covered by close to 1 ML of formate, while the coverage is significantly smaller on (100) and (111).

Fig. 7 (frame c) shows the adsorption free energies of formate as a function of the GCN at a 1/2 ML coverage for the various surfaces. As can be seen, the adsorption free energies scale linearly with the GCN. This allows to estimate adsorption free energies for the corner and edge sites of cuboctahedral particles (see insert in Fig. 7 frame a). For both facets, the adsorption free energy of formate is exothermic and we thus expect a similar behavior as observed for (211), (110) and (321) facets.

Assuming that formate can only be converted to methanol, this would indicate a strong preference of methanol formation on Cu(211) and Cu(110), which we use here to model the edge sites of the copper nanoparticles. On the other hand, the lower coverage of formate on Cu(111) and Cu(100) might indicate that one or both of these sites are the predominate source for CO formation. Coverages of the carboxyl (COOH^*) intermediate as well as CO^* reveal similar trends and are given in the section S3 of the ESI.† These findings roughly correlate with the analysis of the fraction of surface sites shown in Fig. 7 (frame a). This would explain why CO formation strongly decreases for the smallest Cu particles and hence overall the smallest particles give the highest MeOH selectively.

Conclusions

The effect of copper particle size was investigated for CO_2 hydrogenation reaction over carbon-supported copper catalysts with particle sizes between 5 and 20 nm. We found that CO_2 hydrogenation is clearly a structure sensitive reaction. Cu nanoparticles smaller than about 13 nm showed low activity, but high MeOH selectivity. Two distinctly different and particle size-independent activation energy values were found for MeOH and CO formation. DFT calculations revealed that the formation free energy of formate, the main intermediate in methanol formation, is negative on the corner and edge sites, while being positive on terrace sites which are more abundant on larger particles. Therefore, small Cu nanoparticles having a surface dominated by corner and edge sites, have a high ratio of methanol to CO formation, which can be explained by a higher formate coverage. This work is intended to provide new guidelines for the design of novel methanol synthesis catalysts, crucial for the effective utilization of CO_2 .

Author contributions

LB synthesized the catalysts, measured the performance of the catalysts and analyzed the experimental data. LB and PdJ conceptualized the experiments and write-reviewed-edited the manuscript. NV perform the transmission electron microscopy



- 39 F. Studt, M. Behrens, E. L. Kunkes, N. Thomas, S. Zander, A. Tarasov, J. Schumann, E. Frei, J. B. Varley, F. Abild-Pedersen, J. K. Nørskov and R. Schlögl, *ChemCatChem*, 2015, **7**, 1105–1111.
- 40 D. Kopač, B. Likozar and M. Huš, *Appl. Surf. Sci.*, 2019, **497**, 143783.
- 41 F. Calle-Vallejo, D. Loffreda, M. T. M. Koper and P. Sautet, *Nat. Chem.*, 2015, **7**, 403–410.
- 42 Z. P. Liu and P. Hu, *J. Am. Chem. Soc.*, 2003, **125**, 1958–1967.
- 43 S. I. Fujita, S. Moribe, Y. Kanamori, M. Kakudate and N. Takezawa, *Appl. Catal., A*, 2001, **207**, 121–128.
- 44 G. J. J. Bartley and R. Burch, *Appl. Catal.*, 1988, **43**, 141–153.
- 45 A. Karelavic, G. Galdames, J. C. Medina, C. Yévenes, Y. Barra and R. Jiménez, *J. Catal.*, 2019, **369**, 415–426.
- 46 Y. Li, S. H. Chan and Q. Sun, *Nanoscale*, 2015, **7**, 8663–8683.
- 47 M. D. Porosoff, B. Yan and J. G. Chen, *Energy Environ. Sci.*, 2016, **9**, 62–73.
- 48 T. Fujitani, I. Nakamura, T. Uchijima and J. Nakamura, *Surf. Sci.*, 1997, **383**, 285–298.
- 49 S. A. French, A. A. Sokol, S. T. Bromley, C. R. A. Catlow, S. C. Rogers, F. King and P. Sherwood, *Angew. Chem., Int. Ed.*, 2001, **40**, 4437.
- 50 Y. Yang, D. Mei, C. H. F. Peden, C. T. Campbell and C. A. Mims, *ACS Catal.*, 2015, **5**, 7328–7337.
- 51 Y. Yang, C. A. Mims, D. H. Mei, C. H. F. Peden and C. T. Campbell, *J. Catal.*, 2013, **298**, 10–17.
- 52 L. Dietz, S. Piccinin and M. Maestri, *J. Phys. Chem. C*, 2015, **119**, 4959–4966.
- 53 G. Prieto, J. Zečević, H. Friedrich, K. P. De Jong and P. E. De Jongh, *Nat. Mater.*, 2013, **12**, 34–39.
- 54 P. Munnik, M. Wolters, A. Gabrielsson, S. D. Pollington, G. Headdock, J. H. Bitter, P. E. De Jongh and K. P. De Jong, *J. Phys. Chem. C*, 2011, **115**, 14698–14706.
- 55 H. H. Kung, *Catal. Today*, 1992, **11**, 443–453.
- 56 S. Brunauer, P. H. Emmett and E. Teller, *J. Am. Chem. Soc.*, 1938, **60**, 309–319.
- 57 A. L. Patterson, *Phys. Rev.*, 1939, **56**, 978–982.
- 58 G. Kresse and J. Furthmüller, *Comput. Mater. Sci.*, 1996, **6**, 15–50.
- 59 G. Kresse and J. Furthmüller, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1996, **54**, 11169–11186.
- 60 A. H. Larsen, J. J. Mortensen, J. Blomqvist, I. E. Castelli, R. Christensen, M. Dułak, J. Friis, M. N. Groves, B. Hammer, C. Hargus, E. D. Hermes, P. C. Jennings, P. B. Jensen, J. Kermode, J. R. Kitchin, E. L. Kolsbjerg, J. Kubal, K. Kaasbjerg, S. Lysgaard, J. B. Maronsson, T. Maxson, T. Olsen, L. Pastewka, A. Peterson, C. Rostgaard, J. Schiøtz, O. Schütt, M. Strange, K. S. Thygesen, T. Vegge, L. Vilhelmsen, M. Walter, Z. Zeng and K. W. Jacobsen, *J. Phys.: Condens. Matter*, 2017, **29**, 273002.
- 61 J. J. Mortensen, K. Kaasbjerg, S. L. Frederiksen, J. K. Nørskov, J. P. Sethna and K. W. Jacobsen, *Phys. Rev. Lett.*, 2005, **95**, 1–4.
- 62 J. Wellendorff, K. T. Lundgaard, A. Møgelhøj, V. Petzold, D. D. Landis, J. K. Nørskov, T. Bligaard and K. W. Jacobsen, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2012, **85**, 32–34.
- 63 D. Joubert, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1999, **59**, 1758–1775.
- 64 J. Wellendorff, T. L. Silbaugh, D. Garcia-Pintos, J. K. Nørskov, T. Bligaard, F. Studt and C. T. Campbell, *Surf. Sci.*, 2015, **640**, 36–44.
- 65 F. Studt, F. Abild-Pedersen, J. B. Varley and J. K. Nørskov, *Catal. Lett.*, 2013, **143**, 71–73.
- 66 H. J. Monkhorst and J. D. Pack, *Phys. Rev. B: Solid State*, 1976, **13**, 5188–5192.
- 67 P. A. Taylor, P. B. Rasmussen, C. V. Ovesen, P. Stoltze and I. Chorkendorff, *Surf. Sci.*, 1992, **261**, 191–206.
- 68 R. van den Berg, J. Zečević, J. Sehested, S. Helveg, P. E. de Jongh and K. P. de Jong, *Catal. Today*, 2016, **272**, 87–93.
- 69 B. R. Cuenya, *Thin Solid Films*, 2010, **518**, 3127–3150.
- 70 C. Vogt, M. Monai, G. J. Kramer and B. M. Weckhuysen, *Nat. Catal.*, 2019, **2**, 188–197.
- 71 B. S. Clausen, J. Schiøtz, L. Gråbæk, C. V. Ovesen, K. W. Jacobsen, J. K. Nørskov and H. Topsøe, *Top. Catal.*, 1994, **1**, 367–376.
- 72 C. V. Ovesen, B. S. Clausen, J. Schiøtz, P. Stoltze, H. Topsøe and J. K. Nørskov, *J. Catal.*, 1997, **168**, 133–142.
- 73 P. L. Hansen, J. B. Wagner, S. Helveg, J. R. Rostrup-Nielsen, B. S. Clausen and H. Topsøe, *Science*, 2002, **295**, 2053–2055.
- 74 A. S. Crampton, M. D. Rötzer, C. J. Ridge, F. F. Schweinberger, U. Heiz, B. Yoon and U. Landman, *Nat. Commun.*, 2016, **7**, 10389.
- 75 A. Y. Stakheev and L. M. Kustov, *Appl. Catal., A*, 1999, **188**, 3–35.
- 76 A. H. Hakimoun, E. M. Dietze, B. D. Vandegehuchte, D. Curulla-Ferré, L. Joos, P. N. Plessow and F. Studt, *Catal. Lett.*, 2021, **151**, 3165–3169.
- 77 F. Calle-Vallejo, J. I. Martínez, J. M. García-Lastra, P. Sautet and D. Loffreda, *Angew. Chem., Int. Ed.*, 2014, **53**, 8316–8319.
- 78 P. B. Rasmussen, P. M. Holmblad, T. Askgaard, C. V. Ovesen, P. Stoltze, J. K. Nørskov and I. Chorkendorff, *Catal. Lett.*, 1994, **26**, 373–381.
- 79 K. H. Ernst, C. T. Campbell and G. Moretti, *J. Catal.*, 1992, **134**, 66–74.
- 80 J. Nakamura, J. M. Campbell and C. T. Campbell, *J. Chem. Soc., Faraday Trans.*, 1990, **86**, 2725.
- 81 K. Larmier, W. C. Liao, S. Tada, E. Lam, R. Verel, A. Bansode, A. Urakawa, A. Comas-Vives and C. Copéret, *Angew. Chem., Int. Ed.*, 2017, **56**, 2318–2323.
- 82 G. Wang and J. Nakamura, *J. Phys. Chem. Lett.*, 2010, **1**, 3053–3057.

