



Cite this: *Chem. Commun.*, 2020, 56, 9750

Porous materials as carriers of gasotransmitters towards gas biology and therapeutic applications

Arnau Carné-Sánchez,^{id}^{ab} Francisco J. Carmona,^{id}^a Chiwon Kim^{ac} and Shuhei Furukawa^{id}^{*ac}

The discovery of NO, CO, and H₂S as gasotransmitters and their beneficial role in multiple physiological functions opened an era of research devoted to exogenously delivering them as therapeutic agents. However, the gaseous nature of these molecules demands new forms of administration that enable one to control the location, dosage and timing of their delivery. Porous materials are among the most suitable scaffolds to store, deliver and release gasotransmitters due to their high surface area, tunable composition and reactivity. This review highlights the strategies employed to load and release gasotransmitters from different kinds of porous materials, including zeolites, mesoporous silica, metal-organic frameworks and protein assemblies.

Received 26th May 2020,
Accepted 14th July 2020

DOI: 10.1039/d0cc03740k

rsc.li/chemcomm

1. Introduction

Signaling molecules behave as messengers between cells, which trigger subsequent physiological and chemical transformations that are vital for the correct function of organisms. Among these, gaseous signaling molecules, also termed as

gasotransmitters, represent a unique class of signaling molecules because their gaseous nature allows them to diffuse through the cell membrane and to trigger a broad range of catalytic, metabolic processes within a short time after their release. To date, three main gasotransmitters have been identified: nitric oxide (NO), carbon monoxide (CO) and hydrogen sulphide (H₂S).^{1–3} Chronologically, NO was the first gaseous molecule identified as a signaling molecule. In 1987 NO was identified as the endothelium-derived relaxing factor (EDRF) responsible for vein and artery dilation.⁴ Since then, interest in the biological relevance of NO has increased and its biological synthesis from L-arginine by a family of enzymes named as NO synthases (NOS) has been discovered.⁵ Unlike NO, the

^a Institute for Integrated Cell-Material Sciences (WPI-iCeMS), Kyoto University, Yoshida, Sakyo-ku, Kyoto, 606-8501, Japan. E-mail: shuhei.furukawa@icems.kyoto-u.ac.jp

^b Catalan Institute of Nanoscience and Nanotechnology (ICN2), CSIC and Barcelona Institute of Science and Technology, Campus UAB, Bellaterra 08193, Barcelona, Spain

^c Department of Synthetic Chemistry and Biological Chemistry, Graduate School of Engineering, Kyoto University, Katsura, Nishikyo-ku, Kyoto, 615-8510, Japan



Arnau Carné-Sánchez

Arnau Carné-Sánchez was born in Manresa, Catalonia, Spain, in 1985. He received his BSc degree in Chemistry from the Universitat de Barcelona (UAB) in 2008. In 2014 he got his PhD in Chemistry from the UAB under the supervision of Prof. Daniel Maspocho and Dr Inhar Imaz. In 2014 he joined Prof. Susumu Kitagawa and Prof. Shuhei Furukawa's group in iCeMS at Kyoto University (Japan) under a JSPS postdoctoral fellowship. In 2016 he joined ICN2 as a postdoctoral researcher under a Juan de la Cierva fellowship. He is currently researching the synthesis of nano-sized molecular porous materials.



Francisco J. Carmona

Francisco J. Carmona was born in Granada, Spain, in 1987. He received his BSc degree in Chemical Engineering from the University of Granada (UGR) in 2011. In 2017 he got his PhD in Chemistry from the UGR under the supervision of Dr Elisa Barea and Dr Carmen R. Maldonado. In 2017 he joined the research group of Prof. Norberto Masciocchi at Insubria University (Italy). In 2019 he joined Prof. Shuhei Furukawa's group in iCeMS at Kyoto University (Japan). His current research is focused on the development of metal-organic porous frameworks as gas-releasing materials.

biosynthesis of CO from haem degradation catalysed by haem oxygenase (HO) was known long before and for a long time CO was considered as a toxic by-product of metabolism.⁶ The discovery of the biological function of NO triggered a renovated research effort focused on the biological role of CO. These efforts yielded the identification of CO as the second gasotransmitter with an important physiological impact in a variety of processes such as vasodilation, anti-inflammation, anti-proliferation and anti-apoptosis.^{7,8} H₂S was included in the family of gasotransmitters in 2002 and is the last molecule added to this kind of signaling molecules thus far. The presence of H₂S in the organism was already described and, as in the case of CO, its role was supposed to be as a merely noxious toxin.² Further research demonstrated that H₂S is involved in many intracellular signaling pathways with important functions in cytoprotection, anti-oxidation, vasodilation and angiogenesis.^{9,10}

The beneficial effects of gasotransmitters in various physiological functions open the possibility to deliver them exogenously as therapeutic agents. However, all three gasotransmitters identified so far behave as a double-edged sword. They possess acute toxicity at high concentration while they present therapeutic effects at low concentration. In addition, their activity is also dictated by where they are located. For instance, high accumulation of CO or NO in the lungs might result in oxygen replacement in heme and severe hypoxia. On the other hand, vasodilation is induced when these gases are released into blood vessels, which is an effective treatment against coronary diseases. Another example is provided by the anti-inflammatory effect of CO when delivered in the organs or tissue, which postulates CO as a promising non-steroidal anti-inflammatory drug.¹¹

In addition, their gaseous nature implies that challenges related with their handling, storage and appropriate delivery have to be overcome before considering the use of gasotransmitters as drugs. In this context, the use of scaffolds able to immobilize

bioactive gas molecules in solid state (or in solution) and liberate them on demand is highly desirable. Molecules that release bioactive gases gradually or upon external stimuli have been extensively studied and excellent reviews are available.^{12–16} However, the fast diffusion of molecules once administered limits the scope of this strategy as they may cause toxicity to untargeted healthy tissues either by the action of the liberated gasotransmitters or by the release of by-products after gas release. Thus, structuring of gasotransmitters into functional scaffolds in the solid state is a promising strategy to achieve higher payloads of the bioactive gas in targeted areas because they are easier to localize. To date, many kinds of solid-state materials are utilized to release bioactive gases such as inorganic and silica nanoparticles, liposomes and organic polymers.^{17–19} However, in most cases these materials suffer from low payloads, which limits their release capacity. This is due to the fact that only the surface of the materials is available for drug loading (through surface functionalization). A promising strategy to overcome this issue is to use porous materials as functional scaffolds. The high surface area that these materials possess enables incorporation of gasotransmitters not only on their material surfaces but also within the pores, which guarantees a higher drug loading.

The progress in nanomaterials releasing bioactive gases (including gasotransmitters) with specific applications in cancer therapy/bioimaging has been recently revised.²⁰ Here, we analyze the current advances in loading/release of gasotransmitters inside porous materials in the nano-mesoscale (*i.e.* zeolites, mesoporous silica, metal–organic frameworks and protein assemblies) toward a broader variety of bio-applications. The existing gas-releasing materials are classified according to the porous component, as well as to the specific strategy used to load the gas inside them.

2. Strategies to load gases into porous materials

To incorporate gasotransmitters or gas-donor molecules into porous materials one can choose among several strategies. However, the loading methodology will influence not only the loading efficiency but also the rate of release and stimuli that will trigger the release. We categorized the existing methodologies to incorporate bioactive gases into porous materials as follows (Fig. 1):

(1) Use of open metal sites (OMSs) as binding moieties. All porous materials listed here can incorporate metal ions into scaffolds and expose an unsaturated coordination site on metal ions as an OMS. The three gasotransmitters, NO, CO and H₂S, have a strong coordination capability to metal ions, and thus, can be anchored on the pore walls of materials containing OMSs.

(2) Use of the catalytic properties of the OMSs to trigger chemical reactions that produce gasotransmitters as products. OMSs can be used not only as an anchoring site, but also as a catalytic site. In this case, the porous material behaves similarly to an enzyme, which generates a gasotransmitter from a bio-available substrate or an exogenous pro-drug.



Shuhei Furukawa

Shuhei Furukawa was born in Nagasaki, Japan, in 1978. He received his PhD in chemistry from Kyoto University in 2005 under the supervision of Prof. Susumu Kitagawa. After two years postdoctoral research in the Prof. Steven De Feyter's group at Katholieke Universiteit Leuven, he returned to Kyoto as assistant professor. In 2010 he joined iCeMS, Kyoto University, as associate professor and since 2020 he has been a full professor

at iCeMS. His main interest is particularly synthesis and properties of porous materials, controlling their structures over multiple length scales, and their applications in electronics and cell biology.



Fig. 1 Scheme of the different strategies to prepare gas transmitter-releasing materials based on porous frameworks. The existing combinations between strategy and porous framework are indicated. The nitric oxide molecule is used as a gas model.

(3) Immobilization of donor molecules of gas transmitters on the pores by post-synthetic modification. In this strategy, coordination or covalent bonds are often used to fix donor molecules on the pore walls after forming porous materials.

(4) Physical encapsulation of donor molecules of gas transmitters in porous materials. By taking advantage of porous materials, pro-drugs can be incorporated into the pores. However, due to the low host-guest interaction, the molecules can be leaked out of pores. Several strategies are available to limit the extent of the leakage and will be discussed in this review.

3. Zeolites

Zeolites are a family of crystalline porous aluminosilicates with the general formula $M_{x/n}^{n+}[(AlO_2)_x(SiO_2)_y]^{x-}$. With their well-organized and regular system of channels and pores, zeolites have been applied as ion exchangers, catalysts and molecular sieves.²¹ The non-toxic behavior of zeolites combined with their molecular storage property based on microporosity provides an opportunity to use them as drug carriers.²² The presence of OMSs in zeolites, upon guest removal, is advantageous towards trapping and releasing gas transmitters. Likewise, the inherent OMSs together with the feasibility of generating catalytic sites in their frameworks (e.g. acidic sites) could enable the production of gas transmitters from bioavailable substrates. Even though one can find reports on the adsorption of H_2S and CO in zeolites,^{23,24} they are solely focused on their adsorption for removal applications and not on their release for therapeutic applications. Therefore, in this section the loading and release of NO will be exclusively discussed.

3.1 Coordination on open metal sites

The inherent or post-synthetically generated OMSs in zeolites can act as anchoring points, where gas transmitters can be coordinated. This induces a slower and more controlled release than when gas transmitters are merely physisorbed.

Morris and co-workers demonstrated and quantified the high affinity of NO towards zeolites by means of gas sorption experiments. In these experiments, the Co-exchanged zeolite A (Co-LTA) showed an uptake of 1.7 mmol g^{-1} at 800 mmHg. More interesting is the fact that 76% of NO was not released when the pressure was reduced, which demonstrated the strong affinity of NO towards the OMSs present in the structure (Fig. 2a).²⁵ However, the release of NO could be triggered by water molecules, which have stronger affinity towards open metal sites than NO . Indeed, 1.0 mmol g^{-1} of NO was released from NO -loaded Co-LTA by flowing wet gas (11% relative humidity). In addition, the release kinetics could be tuned by varying the relative humidity of the wet gas. This degree of control of the NO delivery from the zeolite was exploited to probe the biological effect of exogenously delivered NO in cells by testing its role in the inhibition of platelet aggregation. A key step towards the use of NO releasing materials in real world applications is their integration into shaped, easy-handling macroscopic materials. In this context, Balkus *et al.* hybridized NO -loaded Co-LTA crystals with polymeric fibers of polylactic



Fig. 2 NO -releasing systems prepared by the chemisorption of NO to open metal sites in zeolites and their beneficial effects: (a) structure of the cobalt- NO complex in zeolite-A as elucidated by single-crystal X-ray diffraction. Reprinted with permission from ref. 25. Copyright 2006 American Chemical Society. (b) SEM images of electrospun polylactic acid fibers containing 13% of cobalt-Zeolite A. The hybridization of the zeolite into a macroscale material allows one to prepare humidity-triggered NO -releasing bandages with gradual gas release. Reprinted with permission from ref. 26. Copyright 2009 American Chemical Society. (c) Enhanced wound-healing due to the topical application of an ointment containing 33% of NO -loaded Zn-zeolite-A in comparison with the application of the pristine ointment. Reprinted with permission from ref. 28. Copyright 2014 Microbiology Society.

acid (PLA) with a bandage shape (Fig. 2b).²⁶ Interestingly, the hybridization induced a more prolonged release by preventing water from coming into contact with the dispersed crystals. Such hybrid nature offers the opportunity to gain additional control over the NO release rate.

Zeolites can be easily functionalized by exchanging with transition metal ions in their structure. Thus, in addition to Co-LTA, other transition metal ion-exchanged LTA zeolites were evaluated as NO delivery vehicles, such as pristine LTA, nickel, copper, manganese²⁵ or zinc zeolites.²⁷ This tunability of the zeolite composition has an impact on the maximum loading capacity, release kinetics and also the appearance of synergistic effects. For example, the burst antibacterial effect of the NO-loaded Zn-LTA against Gram-negative and Gram-positive bacteria was coupled with the long lasting antibacterial effect of the slowly leached Zn(II) ions from the zeolite. Likewise, its hybridization with macroscopic materials could not only modulate the properties of the resulting materials, but also favor its development toward real applications. In this regard, Joshi *et al.* developed an ointment containing 33% of NO-loaded Zn-LTA.²⁸ The hybrid system showed a slower NO release than the pristine NO-zeolite, when suspended in phosphate buffered saline (PBS). The higher hydrophobic character of the ointment hindered NO-exchange with water molecules at the OMSs. This more sustained NO-release resulted in a significant microbicidal activity, and under longer times, against common wound pathogens. Likewise, the topical application of the hybrid ointment was demonstrated to enhance the healing of cutaneous wounds in rats (Fig. 2c). These examples bring to light the feasibility of modulating the release of bioactive agents from zeolites (NO, Zn(II) ions), which determines the biological response. They show the potential of NO-zeolite systems to be incorporated in wound dressing towards the treatment of infected wounds.

Besides the naturally occurring LTA-type of zeolites, titanosilicates have also shown their potential in storing and releasing NO. These materials possess stoichiometric amounts of OMSs in their structures, which largely affect the adsorption and release of NO. Rocha and co-workers focused on the OMSs of the titanosilicate ETS-4 ($[(\text{Na}_9\text{Si}_{12}\text{Ti}_5\text{O}_{38}(\text{OH})\cdot x\text{H}_2\text{O})]$), which is based on pentacoordinated Ti(IV).²⁹ In order to systematically study the impact of the OMSs on the performance of titanosilicates, ETS-4 was compared with ETS-10 ($[(\text{Na},\text{K})_2\text{Si}_5\text{TiO}_{13}\cdot x\text{H}_2\text{O}]$), which possesses only fully coordinated (hexacoordinated) Ti(IV). As expected, ETS-4 largely outperformed ETS-10 with respect to uptake (11 wt% and 5.5%, respectively). The further partial replacement of extraframework Na(I) cations by Cu(II) increased slightly the NO loading. However, the post-functionalization led to an increase in the toxicity of the material, probably because of the leaching of the extraframework copper cations.³⁰ Accordingly, they explored the effects of the isomorphic substitution of framework silicon groups in ETS-10 by the less toxic Al(III) and Ga(III) cations.³¹ The exchanged materials offered higher NO payloads than the unexchanged ETS-10, due to the chemisorption of the gas to the exchanged cations, being also higher than the previously

reported Cu(II)-exchanged ETS-4. Furthermore, the Al- and Ga-exchanged materials exhibited a significant lower toxicity than the Cu-ETS-4 analogs and no metal leaching was observed when incubated in cell culture medium.³² Although the properties of titanosilicates as NO-storing solids are promising, the assessment of their ability to regulate biological functions is essential toward their evolution to real therapeutic applications. With this aim in mind, Pinto and co-workers studied the biocompatibility, chemical stability and NO-release in biological medium of the above-mentioned materials. They selected the unexchanged ETS-4 matrix as the most promising material in terms of amount and sustained NO-release, toxicity and stability. NO-loaded ETS-4 proved to elicit biological responses due to NO-release by reversibly inhibiting mitochondrial oxygen consumption in HeLa cells and promote cell migration, highlighting its potential application in wound healing.³²

3.2 Catalysis

As explained in the previous section, great advances have been made in the development of zeolites for storing and releasing NO towards therapeutic applications. However, this strategy has two main drawbacks: (i) the stored gas is finite and only suitable for short-term applications and (ii) the materials usually need to be conserved under special conditions (*e.g.* away from moisture). One alternative is the chemical production of the gas from a bioavailable substrate.

It is known that nitrite reductase enzymes in bacteria transform NO_2^- to NO mediated by Cu(I) metal sites.³³ Based on this, Morris and co-workers prepared Cu(II)-Zeolite-X and Cu(II)-ZSM-5 by extraframework cation exchange.³⁴ The thermal activation of the materials led to generation of Cu(I) sites by self-reduction reaction.³⁵ Although the materials generated a significant amount of NO when suspended in nitrite aqueous solution, the NO production lasted only a few hours. The concurrent action of both water and dioxygen molecules led to the re-oxidation of the Cu(I) centers to Cu(II), inhibiting the further transformation of nitrites to NO. More interesting is the fact that the pre-adsorption of NO resulted in a constant production of NO during 10 h. The exposition of the materials to gaseous nitric oxide results in the chemisorption of NO to the Cu(I) centers. In the presence of water, only a small fraction of the loaded NO is released, while a significant amount of NO is maintained in the material. The irreversibility of chemisorbed NO hindered the interaction of both water and dioxygen with the Cu(I) sites and inhibited their re-oxidation, and therefore, favored the sustained conversion of nitrite to nitric oxide. This demonstrated the cooperative effect of NO adsorption on the NO-production process.

The acidic transformation of nitrites is an alternative route to produce NO. Morris and co-workers studied the effect of the pore size of acidic zeolites on the production of NO from nitrites by testing four different zeolites: Al-UTL, Al-IPC-2, Al-IPC-4 and Al-IPC-6. To this end, they employed the ADOR (Assembly-Disassembly-Organization-Reassembly) method,³⁶ which allows one to selectively control the pore size of the zeolite by altering the linkers between silicate layers. They

observed that the higher the pore size, the larger the amount of NO generated and the faster the kinetics, demonstrating the feasibility of tuning the NO-generation according to the targeted application.³⁷ In another work, Morris *et al.* prepared several acidic and copper-exchanged zeolites based on mordeinite, ferrierite, ZSM-5 and SSZ-13.³⁸ Although all materials were able to produce NO from nitrite sources, the copper-loaded materials showed a higher activity. In addition, given the known presence of cysteine in the body, the ability of the materials to generate NO in a mixture of nitrite/cysteine at biologically relevant concentration was assessed. As the acidic sites were consumed during NO-production, the continuous NO-generation after subsequent addition of the substrate was inhibited. Conversely, the Cu(I) sites were regenerated by the oxidation of the cysteine present in the media, allowing the continuous conversion of nitrite (Fig. 3). Among the different Cu-zeolites, Cu-SSZ-13 showed the best biocompatibility, making it a promising zeolite to use in the body.

4. Mesoporous silica

Mesoporous silica is a porous inorganic solid formed by amorphous silicon dioxide containing periodic arrays of channels and cavities. It has been widely used as a drug delivery platform due to its 2 to 50 nm pore size and biocompatibility.^{39,40} Compared to zeolites (described in Section 3) that store gasotransmitters within their small cavities, mesoporous silica offers new strategies to accommodate gasotransmitters. For example, one can encapsulate gas-donor molecules, much bigger than the gas itself, which can trigger the release of gasotransmitters by different stimuli such as light, heat or ultrasound. This strategy can be enriched by

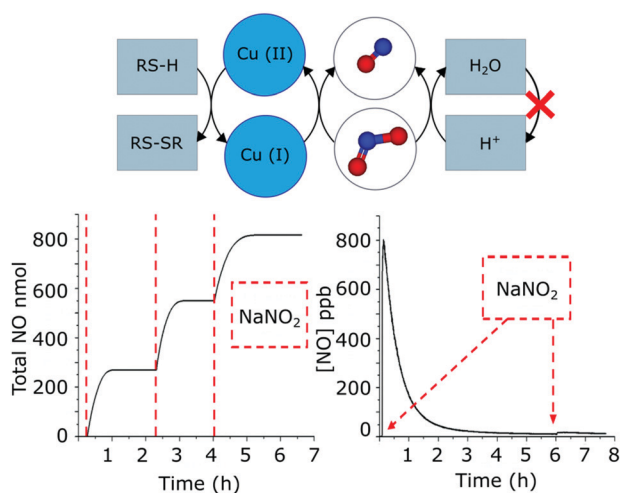


Fig. 3 Scheme of the generation of NO from nitrites mediated by Cu(I) ions and acidic sites in zeolites. Bioavailable compounds like cysteine (RS-H) are able to regenerate the Cu(I) sites, allowing a continuous release after the addition of the substrate (e.g. NaNO₂). In contrast, the acidic groups in zeolites are not regenerated. Therefore, the repeated addition of the substrate does not result in a continuous release of NO when the active sites are consumed. Adapted from ref. 38 with permission from The Royal Society of Chemistry.

the fact that the pore surface can be covalently modified by silanol chemistry.⁴¹ In the following sub-sections, representative works of these two strategies are summarized.

4.1 Encapsulation of gas-donor molecules

The encapsulation of molecules into the pores of mesoporous silica is basically driven by physisorption: the physical interaction between guest molecules and the pore surface of host materials. Consequently, encapsulated guest molecules can escape from the pores by diffusion due to the lack of strong chemical bonding. Therefore, the extent of leaching is the most important issue in this strategy.

To prevent the escape of guest molecules, Rickus and co-workers used liposome vesicles as capsules for NO donor molecules.⁴² Liposomes, phospholipid bilayer vesicles, are also widely used as drug nanocarriers because they prevent the leaching of the entrapped molecule.^{43,44} *S*-Nitroso-*N*-acetylpenicillamine (SNAP), which is known to be a light-induced NO donor molecule, was encapsulated into liposomes, followed by doping them into the synthetic solution of the mesoporous silica. The sol-gel reaction of this mixture containing SNAP, liposomes and tetraethyl orthosilicate (TEOS) provided the liposome/mesoporous silica composite materials. Therefore, the NO release from the functional substrate was measured by using a self-referencing amperometric NO micro-sensor. It was found that the evolution of NO from the mesoporous silica surface was dependent on light irradiation and was within the range of biological relevance (14 pmol cm⁻² s⁻¹).⁴⁵ In addition, the mesoporous silica composite could be used as a functional growth surface for mammalian cells.^{46,47}

Mascharak and co-workers attempted to limit the leaching of NO donor molecules by using host-guest electrostatic interactions.⁴⁸ Thus, they compared the uptake amount of the positively charged metal-nitrosyl NO donor complex ([Mn(PaPy₃)(NO)]ClO₄, denoted as Mn-NO) into a negatively charged aluminosilicate mesoporous material (denoted as Al-MCM-41) and a neutral mesoporous silica material (Si-MCM-41). Al-MCM-41 showed 20% higher uptake when compared to Si-MCM-41 (Al-MCM-41: 2.39 wt%, Si-MCM-41: 2.04 wt%). In addition, Al-MCM-41 showed less leaching of Mn-NO than Si-MCM-41 in saline solution after 24 h incubation (2.92% and 3.44% of adsorbed Mn-NO was leached from Al-MCM-41 and Si-MCM-41, respectively). The mechanism of Mn-NO loading into Al-MCM-41 was supposed to entail cation exchange between [Mn(PaPy₃)(NO)]⁺ and Na(I) ions inside the host and passive diffusion. On the other hand, passive diffusion was the only driving force for Mn-NO loading into Si-MCM-41. Congruent with the higher loading capacity of Al-MCM-41, its release amount of NO by light irradiation was also higher than Si-MCM-41 (0.43 mmol g⁻¹ for Al-MCM-41 and 0.30 mmol g⁻¹ for Si-MCM-41). The control on NO release from Al-MCM-41 allowed studying its antibiotic effect on *A. baumannii*, a skin and soft-tissue infection (SSTI) model showing effective clearance upon light-triggered NO release (Fig. 4a).

Zhao and co-workers took advantage of the porosity of mesoporous silica to accommodate a photolytic NO-donor

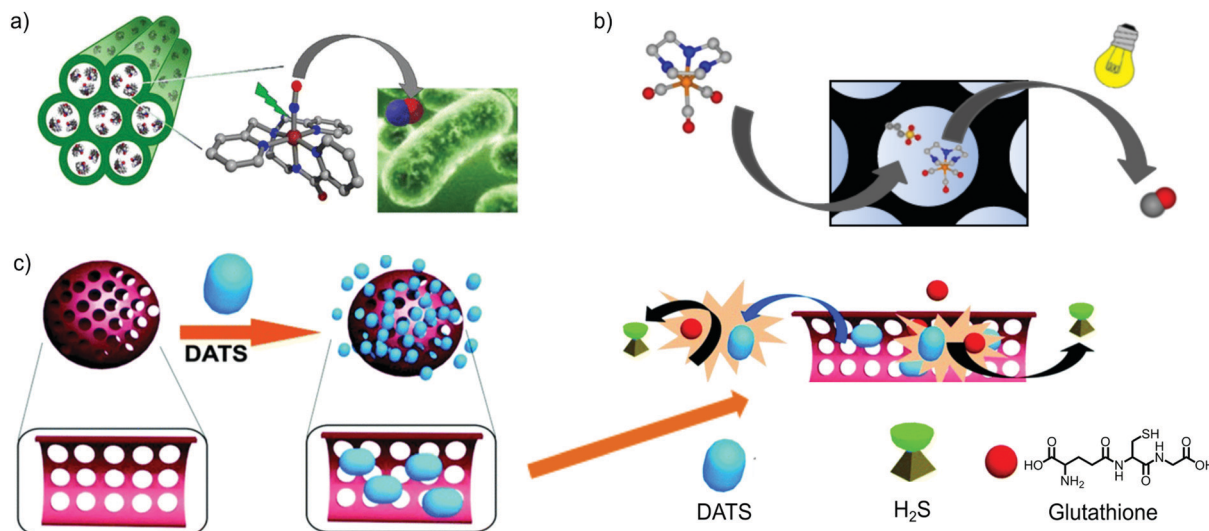


Fig. 4 Gas-releasing frameworks prepared by the encapsulation of gas donors into the cavities of mesoporous silica. There exist examples of gas-donor@Mesoporous silica systems for all gasotransmitters (e.g. CO, NO and H₂S), demonstrating the high versatility of mesoporous silica to prepare gas-releasing materials by means of the gas-donor encapsulation strategy. (a) Representation of Al-MCM-41 mesoporous silica loading the cationic [Mn(PaPy₃)(NO)]⁺ complex. The irradiation with visible light elicits the NO-release response, exerting an antibiotic effect against a skin pathogen (e.g. *A. baumannii*). Reprinted with permission from ref. 48. Copyright 2012 American Chemical Society. (b) Encapsulation of the cationic photoCORM [Mn(tacn)(CO)₃]⁺ into mesoporous silica functionalized with anionic sulfonic groups. The photoresponsive properties of the pristine CORM are maintained and the hybrid material releases CO under photoactivation with visible light. Adapted with permission from ref. 51. Copyright 2016 American Chemical Society. (c) Schematic representation of the encapsulation of Diallyl trisulfide (DATS) in mesoporous silica. The interaction of DATS with the bioavailable glutathione results in the release of H₂S. The slower diffusion of glutathione inside the pores and DATS outside the pores enables a more controlled release of H₂S. Reproduced from ref. 56 with permission from The Royal Society of Chemistry.

[[NH₄][Fe₄S₃(NO)₇], Roussin's Black Salt) in a core-shell upconversion nanoparticle@mesoporous silica nanocomposite.⁴⁹ Irradiation of the nanoparticles with low-damage near-infrared irradiation ($\lambda = 980$ nm, within the therapeutic window) activated the NO-release, being only possible for the bare NO-donor under higher energetic irradiation. By modulating the laser output power, the amount of gas generated was controlled, resulting in a dose-controlled NO-release system. This feature was later demonstrated by *in vitro* cell studies, where different biological responses with NO-dose dependence were achieved by simply tuning the irradiation power of the NIR light used as a trigger.

Mesoporous silica can also be employed as a vehicle to transport guest drugs to the targeted tissue. In addition, the extent of the leaching of the encapsulated NO-prodrug could enable a more sustained NO-release. This strategy was employed by Deng *et al.* toward the efficient treatment of Primary Open-Angle Glaucoma (POAG).⁵⁰ Nitric oxide has proved to reduce elevated intraocular pressure (IOP), a strong risk factor for developing POAG. Likewise, sodium nitroprusside (SNP), a N-donor, has been proposed as a potential therapeutic agent against this disease. However, its low uptake through the cornea together with its poor stability limits its practical use. The encapsulation of SNP inside mesoporous silica resulted in a slower release of the N-donor in PBS, extended during 50 hours. *In vivo* studies on Cav1 gene knockout mice demonstrated that SNP@mesoporous silica nanoparticles were able to pass through the cornea and reach the target tissues. In addition, the topical eye drop application of

SNP@mesoporous silica (0.004 mg of SNP) resulted in IOP reduction of 22% after 3.5 h, followed by a sustained IOP reduction during 48 h. In contrast, the dose of the same amount of SNP solution did not affect IOP, demonstrating the beneficial effect of NO-donor encapsulation.

CO-prodrugs, known as CO-releasing molecules (CORMs), have also been incorporated into the cavities of mesoporous silica to generate CO-releasing materials. For instance, Barea and co-workers functionalized the pore surface of MCM-41 and SBA-15 mesoporous silica with alkanesulfonic groups to confer an anionic character to the frameworks. By cation exchange, they successfully encapsulated the cationic photoactive CO releasing molecule (photoCORM) [Mn(tacn)(CO)₃]⁺ (where tacn is 1,4,7-triazacyclononane), which could not be encapsulated into the neutral matrices (Fig. 4b). Both hybrid materials kept the photoactivity of the pristine CORM, but offering a more sustained CO-delivery kinetics in physiological media when irradiated with white light. Unfortunately, the host-guest interactions were not strong enough and led to partial leaching of the cationic CORM when incubated in saline buffer.⁵¹

As was done with the NO-donor ([Mn(PaPy₃)(NO)]ClO₄, Mascharak *et al.* also used the cation exchange strategy to incorporate a cationic photoCORM into the negatively charged Al-MCM-41 nanoparticles (approx. 60 nm).⁵² For this, the manganese carbonyl complex (*fac*-[Mn(pqa)(CO)₃]⁺, pqa = (2-pyridylmethyl)(2-quinolylmethyl)amine), denoted as Mn-CO, was exchanged with the Na(l) ions presenting in the initial Al-MCM-41 structure. In this case, the host-guest electrostatic interactions ensured a small percentage of leaching when the

composite was incubated in PBS (*i.e.* 2% and 12% of Mn(I) leaching after incubating for 24 h and 60 h, respectively). The released CO from the [Mn-CO]@Al-MCM-41 nanoparticles upon light irradiation was used to induce vasorelaxation of rat aorta muscle rings. A similar strategy was employed to incorporate the luminescent photoCORM [Re(CO)₃(pbt)(PPh₃)], pbt = 2-(2-pyridyl)-benzothiazole) into the pores of Al-MCM-41.⁵³ In this case, not only the intracellular delivery of biologically relevant amounts of CO was demonstrated, but also the nanoparticles could be easily tracked inside the cells, owing to their inherent luminescence. The good encapsulating features of the anionic Al-MCM-41, its stability in physiological media and its large pores were exploited by Barea and co-workers to encapsulate both photoCORM [Mn(tacn)(CO)₃]⁺ and cisplatin within the same carrier, suggesting the possibility of producing CO releasing solid platforms with multiple therapeutic effects.⁵⁴ Diallyl trisulfide (DATS) is known as a glutathione (GSH)-triggered H₂S donor; however, its fast release kinetics hinders its therapeutic use as a rapid increase of H₂S concentration may have adverse effects on the metabolism.⁵⁵ Wang and co-workers encapsulated DATS inside mesoporous silica nanoparticles in order to control the release kinetics of H₂S (Fig. 4c).⁵⁶ DATS was loaded into mesoporous silica nanoparticles (MSNs) by stirring a mixture of DATS, MSNs and distilled water for 12 h. Surprisingly, 99% of DATS molecules were encapsulated into MSNs (which accounts for a loading of 2.5 mmol g⁻¹). This very high loading indicates that there is a strong interaction between DATS and Si-OH of the MSN surface. The low leaching (less than 10%) observed upon 24 h incubation in PBS further supported this hypothesis. The H₂S releasing experiments performed in the presence of GSH showed slower release kinetics from the composite nanoparticles in comparison with free DATS. The biomedical applications of the DATS-MSN nanoparticles were demonstrated by injecting them into mouse's veins. The nanoparticles effectively released H₂S into the vein without causing any of the adverse effects caused by high concentration of H₂S (such as an increase in blood pressure and heart beat rate). Later, the same group demonstrated that the hybrid system DATS@MSNs promoted the proliferation and differentiation of endothelial cells *in vitro* and alleviated inflammatory response caused by hypoxia-reoxygenation. Likewise, *in vivo* studies in mouse models confirmed these benefits, showing that DATS@MSN was able to protect the endothelium of aortic allografts from ischemia-reperfusion injury.⁵⁷

4.2 Chemical attachment of gas donors

The diversity of chemical functionalities that one can use in the sol-gel process (amine, hydroxyl and carboxylate groups among others) enables functionalization of mesoporous silica through post-synthetic reactions. One can use this chemistry to covalently attach donor molecules of gasotransmitters on the surface of these materials. This approach has the disadvantage that it generally involves a multi-step chemical reaction. On the other hand, it reduces the extent of leaching due to the covalent

interaction between the donor and the surface of the mesoporous silica.

Surface modification of mesoporous silica with coordination complexes has been researched by a number of groups in the late 1990s and the early 2000s.^{58,59} Since then, surface modified fumed silica, silica gel and silica nanoparticles have been extensively developed and applied in the field of gas biology.⁶⁰⁻⁶² Longhinotti *et al.* immobilized *cis*-[Ru(bpy)₂(L)NO]³⁺ and [Fe(CN)₄(L)NO]⁻ complexes on surface functionalized mesoporous silica.⁶³ The procedure entailed four sequential surface functionalization reactions, including amine functionalized mesoporous silica (Si-APTS), amine terminal converted to isonicotinamide (ISN) and Ru(II) and Fe(II) metal complex immobilization on the surface of Si-APTS-ISN by reacting the functionalized silica with *cis*-[Ru(bpy)₂Cl₂] and Na₂[Fe(CN)₄(dms₂)₂], respectively. Finally, metal-nitrosyl functionalities were introduced by bubbling NO gas into the prepared silica materials in acetone. Light-induced release of NO in the PBS from both the prepared materials was estimated to be 1.8 mmol g⁻¹.

An alternative moiety that is able to store and deliver NO is the amine group, which can store NO in the form of nitrite and release it under acidic conditions. To immobilize the amine functionality on the surface of mesoporous silica, γ -aminopropyltriethoxysilane (APTES) was attached on the surface of MCM-41 and mesoporous MFI zeolite,⁶⁴ which was synthesized from MCM-41 by dry-gel conversion.⁶⁵ Before the modification of APTES, NO was loaded on MCM-41 and MFI zeolite, which released 0.77 and 0.67 μ mol g⁻¹ of NO in the acidic aqueous solution, respectively. In contrast, APTES modified MCM-41 and MFI zeolite showed a release of 27.43 and 17.99 μ mol g⁻¹, respectively. The higher release observed in the case of MCM-41 is attributed to its higher surface area, which implies a higher degree of surface functionalization. This high release amount in acidic conditions postulates these functionalized materials as efficient NO delivery vehicles for the gastrointestinal organs. The functionalization of the porous framework of mesoporous silica with aminosilanes was also employed by Schoenfisch *et al.* to generate novel NO-releasing materials.⁶⁶ They prepared mesoporous silica with different particle size (ranging from 30 to 1100 nm) and functionalized covalently the pores with terminal secondary amines. By reacting with NO, they were transformed into *N*-diazoniumdiolates able to release NO in physiological media. The materials showed different NO-payloads and release kinetics in PBS. However, these differences could not be correlated with the distinct particle size of the carriers. A further analysis by powder small-angle X-ray scattering (SAXS) suggested that the different pore structures found in the functionalized systems determined these features. While a more ordered pore system enhanced the diffusion of water through the cavities, resulting in faster NO-release kinetics, more heterogeneous pore structures hindered the solvent diffusion and resulted in more sustained NO-release profiles. In another work,⁶⁷ the amine groups in the outer surface of NH₂-functionalized mesoporous silica were used to covalently attach erythrosine, a singlet oxygen photosensitizer (PS), while the internal surfaces were

release gasotransmitters, or that are themselves gasotransmitter donor moieties that can be activated upon external stimuli.

5.1 Coordination on open metal sites

The presence of OMSs decorating the pores of MOFs has shown great potential for selective adsorption of molecules with lone pair of electrons and, as in the case of zeolites, OMSs can be used to store and release gasotransmitters.⁷⁷

Morris and co-workers were pioneers in exploiting the OMSs in MOFs to incorporate NO.⁷⁸ In the first study, $[\text{Cu}_3(\text{btc})_2]_n$ (btc = 1,3,5-benzentricarboxylic acid, also known as HKUST-1), which has Cu(II) OMSs, was used. The first evidence of Cu–NO coordination was provided by the NO sorption isotherms. These isotherms were characterized by a hysteresis in the desorption branch. The number of NO molecules that were not desorbed corresponded to the predicted number of OMSs in the HKUST-1 structure (*i.e.* 2.21 mmol g^{-1}). Further evidence was provided by infrared spectroscopy performed in the NO-loaded HKUST-1, which showed the characteristic peak at 1887 cm^{-1} corresponding to the stretching vibration mode of NO coordinating to Cu(II) ions. The release of NO was triggered by treating the sample with water vapor, similar to the case of zeolites described in Section 3. However, a moderate release of 2 $\mu\text{mol g}^{-1}$ corresponding to 0.1% of the initially adsorbed NO was found. The low NO release is rationalized by the strong coordination of the Cu–NO bond. Despite the low release efficiency, the release amount was enough to inhibit platelet aggregation confirming the potential of MOFs in the field of gasotransmitters release.

Suitable coordination strength between the metal and NO is a key factor to obtain a material that performs well over the whole adsorption-storage-delivery cycle. In order to study the influence of the transition metal ions on the NO release, the same research group employed isostructural MOFs containing different metal ions for the adsorption/release of NO. Namely, they used $[\text{Ni}_2(\text{dobdc})]_n$ (denoted as CPO-27-Ni, dobdc = 2,5-dioxido-1,4-benzenedicarboxylate) and $[\text{Co}_2(\text{dobdc})]_n$ (denoted as CPO-27-Co) for NO storage and delivery (Fig. 6a).⁷⁹ CPO-27-Ni and CPO-27-Co showed a total NO uptake of 7 mmol g^{-1} and 6 mmol g^{-1} , respectively, at 25 °C and 6 mmol g^{-1} and 5 mmol g^{-1} , respectively, of hysteresis in the desorption branch, which correspond to the number of OMSs in each structure. These results indicate that most of NO was adsorbed through coordination to the OMSs and approximately 1 mmol g^{-1} of NO was physically adsorbed to the frameworks. Crystal structures of both frameworks⁸⁰ clearly show that NO is coordinated to metal sites with a bent geometry, which corresponds to NO acting as a one-electron donor. NO release from CPO-27-Ni and CPO-27-Co was triggered by wet gas (11% relative humidity). Unlike HKUST-1, these two MOFs released practically the same amount of NO as previously adsorbed. It is noteworthy that a NO release capacity of 7 mmol g^{-1} is the highest reported value for porous materials thus far. In order to test the biomedical applications of these materials, the vasodilation of pre-contracted pig coronary arteries induced by NO-loaded CPO-27-Ni was tested. The results showed a rapid relaxation of pig

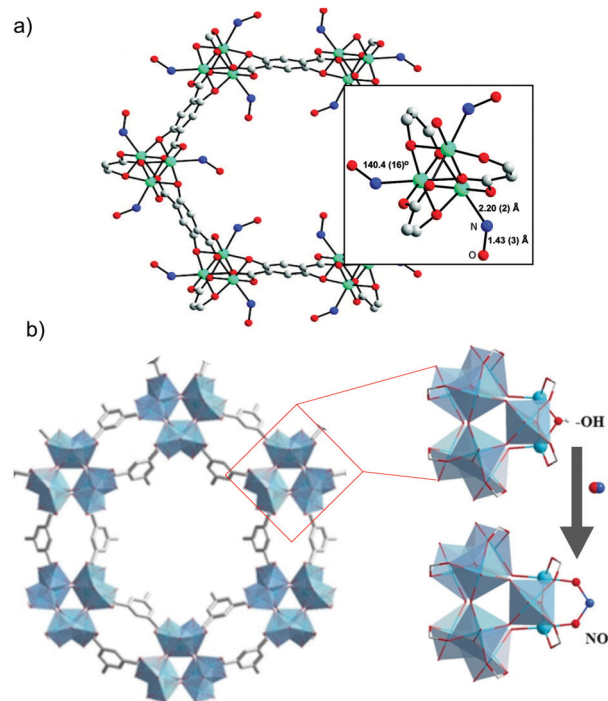


Fig. 6 Examples of NO-releasing metal-organic frameworks showing open metal sites. (a) Crystal structure of the $[\text{Co}(\text{C}_8\text{H}_2\text{O}_6)(\text{NO})_2]$ MOF prepared by the chemisorption of nitric oxide to the unsaturated-cobalt sites. In detail, the view of NO bound to the cobalt atoms in the MOF structure. Reprinted with permission from ref. 79. Copyright 2008 American Chemical Society. (b) Schematic representation of the formation of chemisorbed nitrates on the titanium-based MOF $\text{Ti}_{12}\text{O}_{15}(\text{mdp})_3(\text{OH})_6(\text{H}_2\text{O})_6$. Reprinted with permission from ref. 89. Copyright 2020 John Wiley & Sons, Inc.

coronary arteries immediately after exposing them to an aqueous suspension containing pellets of CPO-27-Ni.

The possibility to synthesize CPO-27 analogue structures with different divalent metal ions enabled one to systematically study the effect of the nature of the OMSs on the adsorption and release of NO.⁸¹ Long and co-workers reported the NO loading and releasing properties of CPO-27-Fe (based on Fe(II)).⁸² Interestingly, while the loading capacity was similar to the examples shown above (*i.e.* 6 mmol g^{-1}), the releasing profile was different, showing an initial burst release followed by a slow and sustained release of NO that occurs over the course of 10 days. These results further prove the key role of the OMSs in the loading and releasing profiles of NO.

A unique feature of MOFs is that they combine OMSs with tunable microporosity. Therefore, one can take advantage of these properties to design multifunctional carriers, delivering more than one substance. Barea and co-workers explored this strategy using CPO-27-Ni as the host structure.⁸³ First, the metallodrug with antitumor activity RAPTA-C ($[\text{Ru}(p\text{-cymene})\text{Cl}_2(\text{pta})]$, pta = 1,3,5-triaza-7-phosphaadamantane) was introduced into the pores of the framework by physisorption. Subsequently, NO was loaded into the composite material. Interestingly, the NO loading capacity (6 mmol g^{-1}) remained almost unaltered after the incorporation of RAPTA-c, which indicates that the coordination of NO at

the OMSs of the framework was not influenced by incorporated RAPTA-C molecules. Importantly, the release of both bioactive molecules was very similar as in the case in which only one of the molecules was encapsulated, indicating the potential use of MOFs as multi drug delivery vehicles.

One of the key aspects when considering MOFs for biomedical applications is their toxicity both *in vivo* and *in vitro*.⁸⁴ Therefore, the synthesis of MOFs with gasotransmitter releasing properties with non-toxic building blocks is a promising strategy to make these materials more biocompatible. The MIL-88 series of MOFs composed by iron(III) carboxylates combine a non-toxic behaviour and the presence of OMSs, which can be used to capture NO.⁸⁵ Therefore, they are suitable candidates as bio-friendly NO delivery vehicles. Serre and co-workers systematically studied the NO loading/release properties of these materials by synthesizing them with different functionalities $[(\text{Fe}_3\text{OX}(\text{-O}_2\text{C-R-CO}_2\text{-})_3)_n]$, R = terephthalic acid, fumaric acid, 2-nitroterephthalic acid and dobdc; X = F, OH, Cl or $\text{-O}_2\text{C-CH}_3$.⁸⁶ The uptake in all cases fell between 1 and 2.5 mmol g⁻¹. However, the release amount was limited in the range of 0.1 mmol g⁻¹ due to the narrow pores in the structure and the strong binding of Fe-NO. In order to improve the NO releasing capacity of the Fe(III) based frameworks, the performance of Fe-MIL-100 (Fe₃OX[btc]₂·xH₂O), which contains big mesoporous cavities within its structure, was evaluated. As expected, the release efficiency was improved when compared to the MIL-88 structure releasing up to 15% of the initially chemisorbed NO (0.35 mmol g⁻¹) over the course of 7 h.⁸⁷ In this regard, the MOF bioMIL-3 [Ca₂(azbz-TC)(H₂O)(DMF)], (azbz-TC = 3,3',5,5'-azobenzene tetracarboxylate), which possesses OMS in its structure, was also assessed as a NO-releasing material due to the high biocompatibility of calcium cations.⁸⁸ It showed a NO payload of 0.8 mmol g⁻¹ and a sustained release during 10 hours under wet nitrogen gas. Recently, Serre and co-workers have proved the feasibility of coordinating NO to the OMSs of a titanium-based MOF, namely Ti₁₂O₁₅(mdip)₃-(OH)₆(H₂O)₆ (mdip: 3,3',5,5'-tetracarboxydiphenylmethane) by the *in situ* formation of complexed nitrites (Fig. 6b).⁸⁹ After a thermal treatment, bridged Ti-OH-Ti groups were generated in the secondary-building units, which after reacting with NO formed chemisorbed nitrites (NO payload of 1.3 mmol g⁻¹). The material showed a slow NO release when suspended in PBS, not previously observed in NO-releasing MOFs due to the lability of the metal-NO bonds and/or the low stability of the frameworks in physiological media. In this case, given the high stability of the MOF, the sustained release was associated to the water-exchange of the chemisorbed nitrites. The material inhibited mitochondrial respiration in a concentration-dependent manner, demonstrating the control of the NO-releasing amount. The treatment of HeLa cells with the NO-releasing material favored the migration of the cells compared to the unloaded one, postulating its employment in wound-healing applications.

As mentioned above, all three gasotransmitters have lone pair electrons. Therefore, it is possible to use OMSs in MOFs to store and deliver not only NO but also CO and H₂S. N. Metzler-Nolte

and co-workers used the MIL-88 (Fe) analogues for CO adsorption and release.⁹⁰ *In situ* ultrahigh vacuum-FTIR and Mössbauer spectroscopy studies of MIL-88B and MIL-88B-NH₂ confirmed the presence of Fe(II)-CO and Fe(III)-CO coordinations after the desorption cycle. In addition, the effect of the ligand functionality was also studied. It was found that the binding strength decreased in the case of MIL-88B-NH₂ due to the electron donating effect of the amino group. Quantification of CO release was carried out through the myoglobin assay under physiological conditions in phosphate buffer at pH = 7.4.⁹¹ The CO release for bare MIL-88B and the amino functionalized version was 0.36 mmol g⁻¹ and 0.69 mmol g⁻¹ respectively. These values are consistent with the higher coordination strength in the Fe-CO bond in the case of the unfunctionalized MIL-88B.

Morris and co-workers further widened the scope of MOFs in the delivery of gasotransmitters by incorporating H₂S in the structure of CPO-27-M (M = Ni, Zn).⁹² In close analogy to the case of NO, H₂S was coordinated to the OMSs of both frameworks showing a maximum uptake close to 6.2 mmol g⁻¹. The differences between the Ni and Zn analogues appeared in their releasing performance. While the H₂S releasing capacity of CPO-27-Ni was 1.8 mmol g⁻¹, in the case of CPO-27-Zn it was 0.5 mmol g⁻¹. This difference is attributed to the difference in the coordination strength between the OMSs and H₂S. The capacity of CPO-27-Zn to store H₂S and release it under physiological conditions enabled testing its vasodilation-induced properties in pre-contracted pig arteries. The immersion of the pre-contracted arteries in an organ bath containing H₂S-loaded CPO-27-Zn resulted in an artery relaxation of 39%.

5.2 Catalysis

OMSs located inside MOFs can be used as catalytic sites, which are easily accessible by the substrates owing to the intrinsic porosity of MOFs. Owing to these complementary properties, MOFs have shown outstanding potential as catalysts.⁹³ On the other hand, several catalytic mechanisms of NO release by decomposition of RSNO are widely known including the copper-mediated pathway.⁹⁴

Reynolds and co-workers used the Cu(II) OMSs in the HKUST-1 structure to catalyze the decomposition reaction of S-nitrosothiols into NO. Thus, HKUST-1 and S-nitrosocysteine (CysNO) were suspended in an ethanolic solution and the NO generation was monitored. It was found that when the MOF was present the NO generation was sustained over the course of 12 h. In contrast, when only Cu(II) salts such as CuCl₂ and Cu(CH₃COO)₂ were employed only a burst release was found. These results suggest that the combination of OMSs and narrow pore architecture is responsible for the sustained NO release.⁹⁵

A further step towards the integration of the catalytic NO releasing property into functional materials was provided by the same authors. To this end, HKUST-1 was immobilized in cotton fabrics to produce NO on the surfaces.⁹⁶ The composite material was shown to be active in the catalytic decomposition of S-nitrosocysteamine (CysamNO) to produce NO. In fact, a NO release of 7.1 mmol g⁻¹ was found over a period of 4 h in

amines under the high pressure of NO gas and releases two molecules of NO by acid-catalyzed spontaneous decomposition with the first-order kinetics, and thus the releasing rate of NO can be precisely predicted. Moreover, its decomposition rate can be tuned by subtle changes in its structure.¹⁰³ Therefore, many kinds of NONOate derivatives, which have various half-lives ranging from few seconds to several hours, have been tested in experimental models of cardiovascular diseases.

Rosseinsky and co-workers were the first to synthesize the NONOate moiety inside a framework structure.¹⁰⁴ In this study, a two-step post synthetic modification of HKUST-1 was implemented. First, 4-(methylamino)-pyridine (denoted as 4-map) was coordinated to the OMSs. Subsequently, the secondary amines were converted to the NONOate functionality by reacting them with NO gas at high pressure. This second step was conditioned by the first step. The reaction did not occur when the loading of 4-map was close to 100% due to the pore blocking effect. On the other hand, the reaction proceeded when the loading was lower than 60%. As a proof of concept, the NO delivery was confirmed in deionized water. However, the NO release was accompanied by significant leaching of 4-map. Cohen and co-workers simplified the strategy by implementing it in two different MOFs, which contain the 2-aminoterephthalate moiety in their structure.¹⁰⁵ Therefore, the NONOate functionality was introduced into $[\text{Zn}_4\text{O}(\text{NH}_2\text{-bdc})]_n$ (denoted as IRMOF-3)¹⁰⁶ and $[\text{Zn}_4\text{O}(\text{NH}_2\text{-bdc})(\text{btb})_{4/3}]_n$ (denoted as UMCM-1-NH₂, btb = benzene-1,3,5-tribenzoate).¹⁰⁷ The yield of the reaction (NONOate formation) for IRMOF-3 and UMCM-NH₂ was 44% and 83% respectively, which is consistent with the higher porosity of the latter. The release amount of NO in water was moderate in both cases (less than 10%) due to the very rapid degradation of both structures.

The poor hydrolytic stability of the NONOate functionalized MOFs limits their scope as NO releasing vehicles in water (or physiological media). However, they can be employed in the sustained release of NO in solid state upon exposure to humid gas. To this end, a ligand bearing three amine functionalities was employed in the synthesis of the MOF $[\text{Cu}_3(\text{TDPAT})(\text{H}_2\text{O})_3]_n$ framework (denoted as Cu-TDPAT, TDPAT = 2,4,6-tris(3,5-dicarboxylphenylamino)-1,3,5-triazine).¹⁰⁸ The amine functionalities were converted to NONOate functionalities by reaction with NO gas in a similar fashion to previously described for IRMOF-3 and UMCM-1-NH₂. The NO releasing experiments in the solid state revealed that the Cu-TDPAT NONOate released NO when exposed to humid gas (RH = 85%) over the course of 7 days and with a maximum release of 0.175 mmol g⁻¹.

Very recently, Xu *et al.* combined the 4-map@HKUST-1 system, showing NONOate functionalities, with a co-axial core-shell polycaprolactone-gelatin fiber to generate a NO-releasing micropatterned scaffold.¹⁰⁹ While the gelatin shell improves the biocompatibility of the nanofibers, the MOF particles are embedded in the hydrophobic polycaprolactone core, which protects them from water. As a result, the hybrid system shows a more gradual NO-release under incubation in PBS than the pristine NO-loaded 4-map@HKUST-1 system. The copper leaching, due to the degradation of the MOF, is also

more sustained in the case of the hybridized system. Given that both NO and copper ions elicit positive response toward angiogenesis, they tested the micropatterned scaffold as a bandage for wound healing in mice. The NO-loaded scaffold showed a notable reduction of the wound, much higher than the untreated control after 7 days (85.23% and 34.89%, respectively). Significantly, the micropatterned scaffold not loaded with NO shows a better performance than the control (71.9% of reduction vs. 34.89%), confirming the activity of the leached copper ions towards wound healing. This example brings to light the potentiality of hybridizing MOFs with other materials to generate macroscale scaffolds with improved properties towards their real use in gas therapy.

Most of the NO-releasing MOFs discussed so far used humidity (water molecule) to trigger the release. However, humidity is a not an easy to control parameter in real physiological conditions, which implies that the degree of control in the delivery of the bio gas is limited. On the other hand, light is a more suitable stimulus because it is non-invasive and can be manipulated in terms of intensity, wavelength and location. Therefore, the use of photodonor ligands as part of the framework is a promising strategy to develop new photoresponsive gas transmitter releasing materials. Furukawa, Kamei and co-workers first implemented this strategy by using imidazole ligands bearing the nitro functionality in the synthesis of zeolitic imidazole frameworks (ZIF) (Fig. 8a). Aromatic molecules with nitro groups are well known for their NO photogeneration.^{110,111} Thus, the reaction of 2-nitroimidazole (2-nIm) or 5-methyl-4-nitroimidazole (mnIm) with Zn(II) ions yielded $[\text{Zn}(2\text{nIm})_2]_n$ (NOF-1) and $[\text{Zn}(\text{mnIm})_2]_n$ (NOF-2).¹¹² Interestingly, both frameworks showed light triggered NO release in the solid-state with a maximum release of 3 mmol g⁻¹. The light used for these experiments was set at 365 nm. Interestingly, the NO release duration and rate could be controlled by light on/off and intensity. It is noteworthy that the light triggered NO release efficiency of the ligands themselves was significantly lower (less than 0.5 mmol g⁻¹) than the respective frameworks. The difference in photoreactivity between the frameworks and the ligands is attributed to the structuring effect of the frameworks. The spatial segregation of the photoreactive moieties within the framework avoids the aggregation induced quenching observed in the ligands in the solid-state, which paves the way to new solid-state NO releasing materials. The solid-state delivery of NO of NOF-1 crystals enabled their integration into substrates that can then be used as functional extracellular scaffolds. Using this cell culture platform, the spatiotemporal stimulation of cells by NO was demonstrated, which subsequently caused an increase of intracellular Ca²⁺ ion concentration in the genetically modified HEK293 cells with TRPC5 channels.

Besides the nitro aromatic groups, the bis-*N*-nitroso (BNN) moiety is also known to release NO upon light irradiation. However, its low thermal stability prevents its use in the direct synthesis of the MOF. Thus, it must be incorporated in the framework structure by post-synthetic modification through nitrosation of secondary amines. Therefore, two MOFs with



Fig. 9 Schematic representation of the subunit of ferritin with an inner diameter of 8 nm, formation of the $\text{Ru}(\text{CO})_2$ -protein adduct and cellular uptake of the Ferritin- $\text{Ru}(\text{CO})_2$ composite and intracellular CO-release. Adapted with permission from ref. 123. Copyright 2014 American Chemical Society.

introducing a Mn(I) based photoCORM.¹²⁵ Thus, a mutant version of ferritin rich in cysteines was used to coordinate Mn(I) carbonyl species. Interestingly the composite protein assembly released CO only upon light irradiation at 456 nm. Owing to the biocompatible nature of the CO carrier, it could be used as an intracellular CO delivery vehicle. The high degree of control achieved in the CO delivery together with the biocompatibility of the carrier makes this material highly promising to further understand the role of CO at the cellular level.

Very recently, Cai *et al.* designed a novel CO-releasing material based on a self-assembly of fluorinated amphiphilic dendritic peptide (FADP) with a hydrophobic core, co-encapsulating the photosensitizer chlorin e6 (Ce6) and the CO-releasing molecule $[\text{Mn}(\text{CO})_4(\text{S}_2\text{CNMe})(\text{CH}_2\text{CO}_2\text{H})]$ (CORM-401).¹²⁶ As CORM-401 is a H_2O_2 -responsive CORM, the presence of Ce6 enabled indirect control of CO-release by light. Under irradiation at 665 nm in water, Ce6 generates relevant concentrations of $^1\text{O}_2$ and H_2O_2 . The reaction of generated H_2O_2 with the CORM-401 triggers the CO-release. While the fluorinated surface enhances the binding affinity towards bacterial membranes, the co-delivery of CO and $^1\text{O}_2$ exerts a significant synergistic bactericidal effect. *In vitro* and *in vivo* studies proved that the hybrid system showed a high antibacterial activity under NIR irradiation, together with good biocompatibility. Likewise, the hybridized system had a significant activity towards the ablation of biofilms. These features make CORM-401-Ce6@FADP a promising formulation toward its real application as a bactericidal agent.

7. Conclusions and outlook

After nearly fifteen years of multidisciplinary research that combined gas biology and porous materials, the resulting knowledge has led to a versatile toolbox of materials and strategies to load and release gasotransmitters from porous materials. Thus, researchers can tune the stimuli to deliver gases from porous materials as well as to control their release

kinetics to meet the criteria for selected biomedical applications, such as wound healing, vasodilation and anti-inflammation among others.

As we have summarized in this review, zeolites offer a robust and non-toxic framework with well-ordered OMSs being able to store NO that can be spontaneously released through water exchange or produce it *in situ* through catalytic reactions. Therefore, while zeolites excel in the prolonged and spontaneous release of NO, it is challenging to modulate their performance toward NO release on demand because humidity and concentration of reactants cannot be easily modulated *in vivo*. Alternatively, the large pores of mesoporous silica allow encapsulating gas releasing molecules that are sensitive to different stimuli such as light and heat. This strategy offers the advantage of easily incorporating the advances achieved in the field of gasotransmitter-releasing molecules into the porous material field. Thus, mesoporous silica has proven to be a versatile material for releasing all known gasotransmitters through different stimuli, which made it possible to attain important goals in the field of gas biology such as on-demand gasotransmitter release. MOFs provided their versatility in terms of structures, composition and reactivity to the field of gas biology, which enabled the development of novel routes toward the controlled release of gasotransmitters. For example, the incorporation of gas releasing moieties in the organic linker of the MOF not only achieved high payloads of gases but also their light triggered release in the solid-state paving the way for its implementation in novel devices. All these materials share the fact that they are exogenous, which might rise some concerns on their biocompatibility. In this regard, protein assemblies offer inherently biocompatible scaffolds in which to localize gasotransmitters at the cost of providing low payloads and stability.

However, as highlighted in several examples across this review, the successful implementation of porous materials for the therapeutic release of gasotransmitters in the real world application requires an appropriate strategy for their materialization/formulation and administration. Thus, processing of gasotransmitter releasing porous materials into stable colloids, gels, or ointments or shape them into macroscopic objects through hybridization with other materials such as polymers is a promising strategy toward their practical use. All these strategies entail specific challenges that still need to be overcome. For instance, the intravenous administration of the porous carriers implies the use of nanoscopic carriers with narrow size distribution and structural and colloidal stability in physiological media. In this regard, coating the porous carriers with biocompatible polymers and lipids has been shown to be a promising strategy to prevent degradation and increase colloidal stability. Alternatively, the use of non-toxic building blocks held by strong interactions in the synthesis of nanoscopic porous carriers has been shown to increase the stability/biocompatibility of the porous carrier as exemplified by titanosilicates and MOFs made with high valence metal ions (*i.e.* Fe(III), Zr(IV) and Ti(IV)). The synthesis of stable nano-sized porous carriers for gasotransmitters together with further

- 125 K. Fujita, Y. Tanaka, S. Abe and T. Ueno, *Angew. Chem., Int. Ed.*, 2016, **55**, 1056–1060.
- 126 W. Ma, X. Chen, L. Fu, J. Zhu, M. Fan, J. Chen, C. Yang, G. Yang, L. Wu, G. Mao, X. Yang, X. Mou, Z. Gu and X. Cai, *ACS Appl. Mater. Interfaces*, 2020, **12**, 22479–22491.
- 127 A. Carné-Sánchez, G. A. Craig, P. Larpent, T. Hirose, M. Higuchi, S. Kitagawa, K. Matsuda, K. Urayama and S. Furukawa, *Nat. Commun.*, 2018, **9**, 2506.
- 128 N. Giri, M. G. Del Pópolo, G. Melaugh, R. L. Greenaway, K. Rätzke, T. Koschine, L. Pison, M. F. C. Gomes, A. I. Cooper and S. L. James, *Nature*, 2015, **527**, 216–220.
- 129 R. Gaillac, P. Pullumbi, K. A. Beyer, K. W. Chapman, D. A. Keen, T. D. Bennett and F.-X. Coudert, *Nat. Mater.*, 2017, **16**, 1149–1154.
- 130 Y. Hara, K. Kanamori and K. Nakanishi, *Angew. Chem., Int. Ed.*, 2019, **58**, 19047–19053.