Nanoscale Advances



PAPER

View Article Online
View Journal | View Issue



Cite this: Nanoscale Adv., 2020, 2, 2192

A nano-integrated diagnostic and therapeutic platform with oxidation—reduction reactions in tumor microenvironments†

Lei Zhao,^{ab} Guihua Qiu,^a Kai Wang,^a Hu Chen,^a Fengkai Ruan,^a Nan Liu,^a Zifeng Deng,^a Youliang Yao,^a Dongbei Guo,^a Dai Wang,^a Li Sha,^b Xiangyu Kong,^b Wenzhi Liu*^b and Yongxing Zhang ¹ ***

In the present study, we developed a nano-integrated diagnostic and therapeutic platform with oxidation-reduction reactions in tumor microenvironments (TMEs). The proposed platform resolved the contradiction of particle size between the enhanced permeability and retention (EPR) effect and tumor interstitial penetration, as well as poor circulation and low drug-loading efficiency. Flower-like MnO_2 NPs were used as the core and modified with hyaluronate (HA) and H_2PtCl_6 to obtain $MnO_2-HA@H_2PtCl_6$ (MHP). The maximum drug-loading efficiency rate of H_2PtCl_6 reached 35% due to its chelation with HA. MHP showed satisfactory integrity and stability during circulation and can also be used as a magnetic resonance imaging (MRI) contrast agent. In addition, MHP as a radiosensitizer achieved an excellent tumor inhibition effect in combination with radiotherapy. Importantly, MHP released ultra-small nanoparticles, USNPs, (\sim 20 nm) through the supramolecular self-assembly abilities of Mn^{2+} , HA, and H_2PtCl_6 in TMEs, leading to the increase of penetration into multicellular spheres and solid tumors (Scheme), as well as prolonging its retention in tumors.

Received 16th December 2019 Accepted 7th March 2020

DOI: 10.1039/c9na00786e

rsc.li/nanoscale-advances

1 Introduction

The transportation of nanoparticles (NPs) in solid tumors is mainly associated with their diameter and surface potential.¹⁻⁴ A dense extracellular matrix, high interstitial fluid pressure (IFP), and uneven distribution of tumor vessel diameter are the main reasons for poor clinical treatment.^{5,6} NPs with diameters in the range of 60–100 nm have shown a satisfactory enhanced permeability and retention (EPR) effect and high tendency towards extravasation across the tumor vessels, while they cannot uniformly and effectively penetrate into the tumor stroma.^{3,7} The NPs with diameters in the range of 10–20 nm can significantly penetrate into the tumor stroma and spread evenly, while the removal rate is faster, and the retention time of tumor is shortened.⁵

Radiation therapy is a therapeutic method, utilizing ionizing radiation to induce DNA damage to kill cancer cells.⁸ Besides, its disadvantages mainly include lack of selectivity of radiation location and poor efficacy due to the hypoxic regions in solid tumors.⁹

In order to solve the above mentioned problems, radiosensitizers (e.g., gold nanoparticles¹⁰ and titanium oxide nanoparticles¹¹) have been developed. However, a number of these nanoparticles are not biodegradable and cannot be therefore used in clinical practice due to their long-term retention *in vivo*. It has been reported that the nanomaterial perfluorocarbon is helpful to transport oxygen, but there are a number of shortcomings, such as short retention time of oxygen in nanomaterials, low efficiency of oxygen transport, and the need for a particular range of temperature to control and release.¹² It is well-known that high concentration reactive oxygen species (ROS) (e.g., H_2O_2 , $\sim 100~\mu M$) in tumor microenvironments (TMEs) can limit the efficacy of radio-chemotherapy in tumors.¹³ Moreover, M2 phenotype tumor-associated macrophages (TAMs) promote tumor metastasis and drug resistance in hypoxic regions and tumor hypoxic environments.¹⁴

In the present study, we synthesized a biodegradable nanointegrated diagnosis and treatment platform, namely MHP, in order to overcome the above-mentioned problems. For this purpose, hyaluronan (HA), as a hydrophilic polysaccharide, was used to modify the surface of flower-like MnO_2 cores and increase the loading rate of H_2PtCl_6 . MHP is sensitive to oxidation-reduction reactions and has acceptable biocompatibility and can be utilized as an ultra-small nanoparticle (USNP) triggered by TMEs. With consuming excessive endogenous H_2O_2 in TMEs, it degrades from the original parental NPs (100 nm) to USNPs (\sim 20 nm), leading to deeper penetration and longer retention in the tumor stroma. Due to its initial

^aState Key Laboratory of Molecular Vaccinology and Molecular Diagnostics, School of Public Health, Xiamen University, Xiamen, Fujian, 361102, PR China. E-mail: z63y94x@xmu.edu.cn

^bAffiliated Zhongshan Hospital of Dalian University, Dalian, Liaoning, 116001, PR China. E-mail: liuwenzhi196507@163.com

[†] Electronic supplementary information (ESI) available. See DOI: 10.1039/c9na00786e

Open Access Article. Published on 11 2020. Downloaded on 31.10.2025 05:44:38.

Paper Nanoscale Advances

appropriate hydrodynamic diameter (100 nm), MHP has a promising EPR effect. MHP as a radiosensitizer can achieve an effective tumor inhibition in combination with radiotherapy. In addition, by means of multi-elemental and spectral detection, we preliminarily confirmed the basic components of the USNPs by combining different centrifugation and dialysis methods. Our research was conducted on the basis of the formation of USNPs by supermolecular recombination after the metabolism of nanomaterials induced by TMEs, aiming to provide a new idea for penetration of radio-chemotherapy into clinical tumors.

Results and discussion 2

Synthesis and characterization

In the current research, we synthesized MnO2-HA@H2PtCl6 nanoparticles by the layer-by-layer (LBL) method as a nanoscale coating and surface functionalization technique. Next, oleic

acid was utilized to reduce potassium permanganate to obtain flower-like MnO₂ NPs with a size of 70-110 nm (average size: 90 nm) (Fig. 2b), and then, they were characterized by transmission electron microscopy (TEM; Fig. 1a) and (EDS; Fig. S1†).

Afterwards, the HA was adsorbed on the surface of MnO₂ to form MnO2-HA. A number of scholars demonstrated that HA possesses a series of appropriate properties, such as biocompatibility, biodegradability, and non-immunogenicity.^{15,16} TEM revealed that core-MnO2 was surrounded by light-colored substances (Fig. 1b), suggesting that HA has been successfully loaded around the core. Zeta potential almost showed the same surface charge as HA (Fig. 1i), suggesting that the combination of HA and core-MnO₂ is electrostatic adsorption.

Before final loading, we tested the inhibitory effect of H₂PtCl₆ on cancer cells. It was disclosed that treatment with 10 μg mL⁻¹ H₂PtCl₆ could significantly inhibit the proliferation of HCT-116, and treatment with 20 $\mu g \, mL^{-1} \, H_2 PtCl_6$ for 48 h could inhibit cell proliferation by within 45% (Fig. 1e). Additionally,

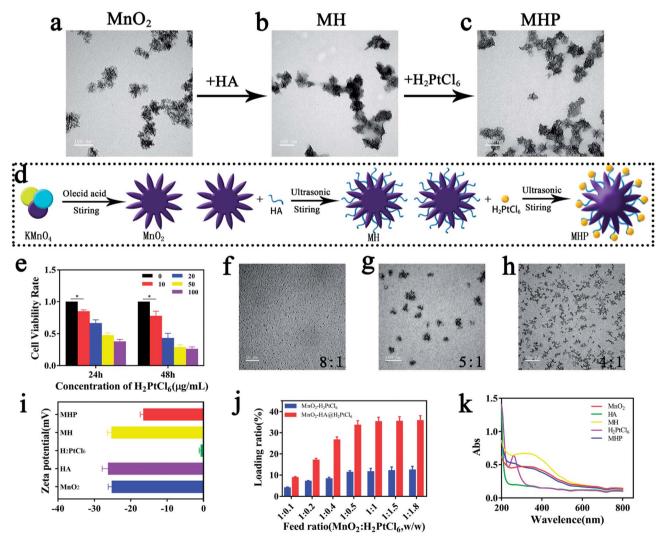


Fig. 1 (a) TEM image of MnO₂ NPs, scale bar: 100 nm; (b) TEM image of MnO₂-HA, scale bar: 100 nm; (c) TEM image of MnO₂-HA@H₂PtCl₆, scale bar: 100 nm; (d) schematic illustration of synthesis of MHP; (e) HCT-116 cell viabilities after incubation with H₂PtCl₆ for 24 and 48 h; (f-h) TEM images of HA-H₂PtCl₆ at different ratios of HA/H₂PtCl₆. The scales are 50, 100, and 200 nm, respectively; (i) zeta potential of MnO₂, HA, H₂PtCl₆, MH, and MHP; (j) loading efficiency of H₂PtCl₆ at different ratios; (k) UV-Vis-NIR of MnO₂, HA, H₂PtCl₆, MH, and MHP. *P < 0.05.

treatment with 20 µg mL⁻¹ H₂PtCl₆ for 8 h could cause cell apoptosis by around 81% (Fig. S2†), in addition to remarkable double-strand breaks in DNA (Fig. S3†). In vitro, different ratios of HA/H₂PtCl₆ might form nanoparticles with different sizes. When the mass ratio turns out to be 8:1, 5:1, and 4:1, the particle size is less than 50 nm (Fig. 1b-d). Moreover, when the proportion of H_2PtCl_6 is excessive (Fig. S4†), a ratio of 1:5 seems to be appropriate to form regular nanoparticles; when the ratio is 1:4, regular nanoparticles cannot be formed; however, when the ratio is 1:8, the proportion of H₂PtCl₆ may be excessive. Hence, we can speculate that the binding of HA to H₂PtCl₆ may be based on the chelation of the Pt-centered atom and HA-ligand.

Eventually, H₂PtCl₆ was added to the surface of MH to form MnO₂-HA@H₂PtCl₆ (MHP). With the help of inductively coupled plasma mass spectrometry (ICP-MS), it was revealed that the drug-loading efficiency of H2PtCl6 was increased with the increase of H₂PtCl₆, and this may be due to high specific surface area of MnO2. Furthermore, when HA was used as the medium, the drug-loading efficiency of H2PtCl6 was

significantly increased, which was about 35% when MnO₂- $: HA : H_2PtCl_6 = 1 : 20 : 1$ (w:w:w, Fig. 1j). As shown in Fig. 1c, the particle size was mainly distributed in the range of 80-120 nm (average size: 100 nm) by dynamic light scattering (DLS) (Fig. 2b). Zeta potential showed that the reduction of negative surface charge was associated with loading of H₂PtCl₆ (Fig. 1i), which may due to the combination of H⁺ with the carboxylate of HA. The successful synthesis of MHP was verified by ultraviolet-visible-near infrared (UV-Vis-NIR) spectroscopy (Fig. 1k) and energy dispersive X-ray spectroscopy (EDS) (Fig. S5†).

2.2 Properties of MHP

The TME has a higher amount of H_2O_2 (~100 μ M) and acidic environment, 17-20 in which MHP can immediately produce a great number of air bubbles, indicating that O₂ was produced rapidly, and simultaneous production of Mn²⁺ which is a strong magnetic resonance imaging (MRI) contrast agent. TEM and DLS showed that MHP could release USNPs (\sim 20 nm) during 30 min (Fig. 2a and b), and the TEM image of that incubated

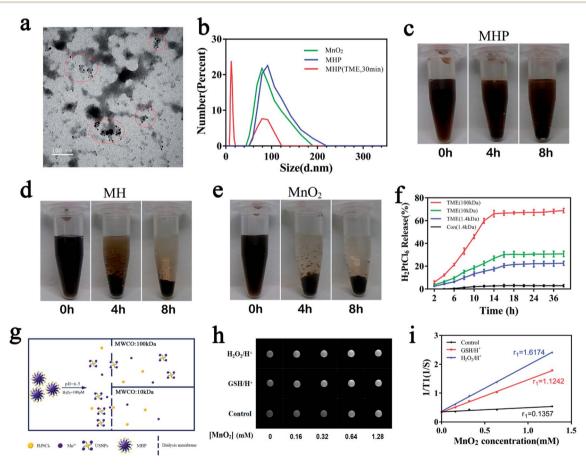


Fig. 2 (a) TEM image and (b) DLS analysis of MHP after incubation in saline at $H_2O_2 = 100 \mu M/pH = 6.5$ for 30 min; (c-e) appearance of MHP, MH, and MnO₂ dispersed in saline at 0, 4, and 8 h, respectively. (f) Cumulative H₂PtCl₆ release of MHP under different conditions via dialysis with molecular weights of 1.4, 10, and 100 kDa, respectively. (TME: $H_2O_2 = 100 \mu M/pH = 6.5$, control: $H_2O_2 = 0 \mu M/pH = 7.4$); (q) USNPs were released from MHP in the TME, and then passed through the dialysis membranes with a molecular weight of 100 kDa, while dialysis membranes with a molecular weight of 10 kDa only allowed Mn^{2+} and H_2PtCl_6 to pass through; (h) T_1 -weighted magnetic resonance imaging (MRI) of MHP, MHP + GSH/H⁺, and MHP + H_2O_2/H^+ ; (i) MRI of the MHP: $1/T_1$ versus MnO₂ concentration for MHP, the MHP + GSH/H⁺, and MHP + H_2O_2/H^+ .

overnight is shown in Fig. S6.† Centrifugation at 16 000 rpm for 10 min and dialysis (14 000 MW) were carried out, and ICP-MS demonstrated [Mn]: [Pt] in the supernatant before dialysis, in the supernatant after dialysis, and precipitation after dialysis, which were (1.27097–1.28031), (1.15368–1.16724), and (1.16223–1.16856), respectively. However, [Mn]: [Pt] was approximately equal to 3.772 in MHP, which showed the release of superfluous Mn²⁺ during transformation. The UV-Vis-NIR did not show the absorption peak of HA in the supernatant after dialysis, suggesting that HA was approximately 100% transformed. Therefore, we can preliminarily speculate that the chemical formula of the USNPs is as follows: $(Mn)_{4n} (H_2PtCl_6)_n (C_{14}H_{20}NO_{11}Na)_x$, which may be formed by the self-assembly of Mn^{2+} , HA, and H_2PtCl_6 .

Next, the stability of the NPs was tested with saline. It was observed that MnO₂ was almost fully aggregated and precipitated during 4 h (Fig. 2e), reflecting a poor hydrodynamic stability, which is consistent with findings of a previous study.²¹ Importantly, MH showed a large amount of precipitation, while MHP revealed nearly no precipitation during 4 h (Fig. 2c and d); after 8 h, MH was almost fully precipitated, whereas MHP only revealed a small amount of precipitation, demonstrating that MHP had superior stability to MnO₂ and MH in saline, and this may be related to the surface charge and dispersion of NPs. Although it was disclosed that the hydrodynamic stability of

MnO₂ NPs has been improved after modifying the HA surface, there are a number of defects in the present study related to a nano-integrated platform, and MHP can be therefore utilized as an alternative.

The ability of MHP to release H_2PtCl_6 in the TME was examined by ICP-MS (Fig. 2f). The release of H_2PtCl_6 was nearly undetectable in a control environment (pH = 7.4, $H_2O_2 = 0 \mu M$, MWCO: 1.4 kDa), which showed an appropriate integrity of MHP. Small amounts of H_2PtCl_6 were released in the TME (pH = 6.5, $H_2O_2 = 100 \mu M$, MWCO = 1.4 kDa), demonstrating that MHP had satisfactory oxidation–reduction reactions. Distinct H_2PtCl_6 released profiles were obtained by dialysis at different molecular weight cut-off values (10k, 100k); thus, we postulated that MHP could partially disassemble into USNPs (~20 nm) in saline in the TME (Fig. 2g).

It is noteworthy that $\rm Mn^{2+}$ released from $\rm MnO_2$ into the TME is an efficient MRI contrast agent.^{22,23} MRI was applied for diagnosis of tumors with a 1.5 T clinical MR scanner at room temperature. Images of the three groups showed different degrees of whitening effects with the increase of the $\rm MnO_2$ concentration (Fig. 2h). The r_1 values after the reaction under glutathione (GSH) (2 Mm, pH 5.0) or $\rm H_2O_2$ (100 $\rm \mu M$, pH 5.0) for 6 h were 1.1242 and 1.6174 mM $^{-1}$ s $^{-1}$, respectively (Fig. 2i), which were 8.28 times (1.1242/0.1357) and 11.9 times (1.6174/0.1357) higher than those in the control group. This indicates that MHP

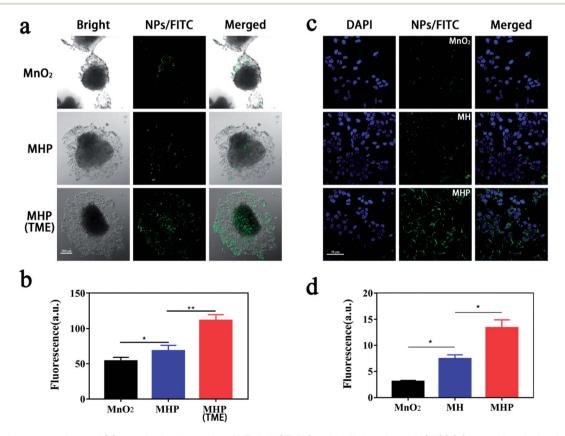


Fig. 3 (a) In vitro penetration and (b) quantitative detection of NPs in HCT-116 multicellular spheroids (MCSs) 6 h post-incubation in saline under different conditions. Green represents FITC-labeled NPs. Scale bar: 200 μ m; (c) NPs were absorbed or associated with cell membranes. Green represents FITC-labeled NPs and blue represents DAPI. Scale bar: 50 μ m; (d) quantitative detection of NPs at 6 h after incubation with HCT-116 cells. *P < 0.05; **P < 0.01.

has a strong T1 imaging function in the TME, and that it is feasible as a positive MRI contrast agent.

2.3 In vitro penetration ability and cellular uptake test

In this stage, a multicellular sphere (MCS) model was used to assess the *in vitro* penetration ability of MHP. We incubated equivalent fluorescein-5-isothiocyanate (FITC)-labeled NPs with MCS under different conditions for 6 h, and their penetration depth was measured by confocal laser scanning microscopy (CLSM) (Fig. 3a). Compared with the MnO₂ group, whose green fluorescence only appeared in small amounts of cells outside the sphere, fluorescence was slightly observed both inside and around the cell sphere in the MHP group. The cellular uptake test showed that NPs absorbed by HCT-116 cells or associated

with cell membranes were MHP/FITC, MH/FITC, and MnO₂/FITC, which ranked from maximum to minimum (Fig. 3c and d). This may be due to the hierarchical dispersion of NPs and CD44 receptors' targeting effect of HA.^{24,25} Importantly, fluorescence in the MCS was the strongest in all groups when incubated in the TME ($\rm H_2O_2=100~\mu M/pH=6.5$) (Fig. 3b), which further indicated that MHP released USNPs under the circumstance of the TME.

2.4 Cytotoxicity assay

We evaluated the *in vitro* cytotoxicity of MH, H₂PtCl₆, and MHP combined with radiation (Fig. 4a). Before any treatment, a small amount of sterile paraffin was covered on the surface of the cell culture medium to simulate the hypoxic environment of

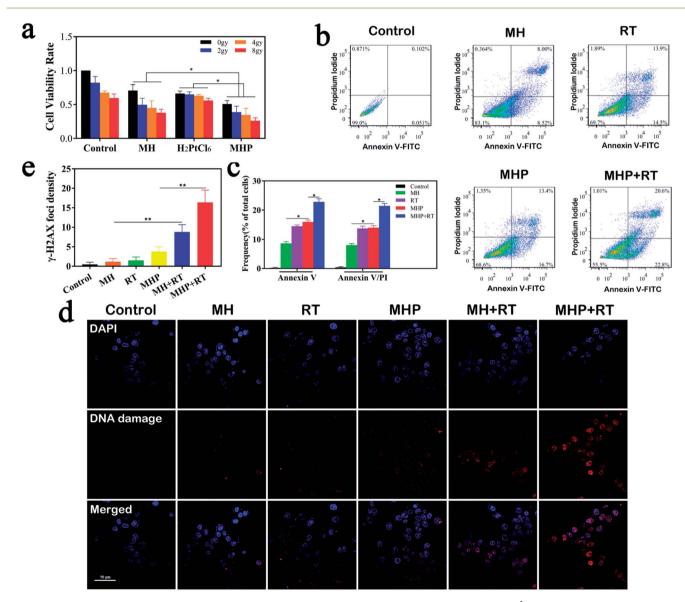


Fig. 4 (a) Cytotoxicity of HCT-116 cells treated with MH, H_2PtCl_6 , and MHP (MnO₂/ $H_2PtCl_6 = 50/17.5 \, \mu g \, mL^{-1}$) at different radiation doses at 0, 2, 4, and 8 Gy; (b) flow cytometry analysis; (c) quantitative analysis of apoptosis induced by MH or MHP (MnO₂/ $H_2PtCl_6 = 50/17.5 \, \mu g \, mL^{-1}$) combined with or without radiation (5 Gy); (d) immunofluorescence staining of γ -H2AX foci in HCT-116 cells treated with saline, MH, and MHP (MnO₂/ $H_2PtCl_6 = 50/17.5 \, \mu g \, mL^{-1}$), with or without radiation (5 Gy). Blue represents DAPI and red represents Cy3 double-strand breaks in DNA. Scale bar: 50 μ m; (e) quantitative analysis of γ -H2AX foci (γ -H2AX foci/100 μ m²) for n > 100 cells in each treatment group. *P < 0.05; **P < 0.01.

tumors. The results showed that the cell proliferation rate gradually decreased in all the groups with the increase of irradiation dose. Additionally, MHP with the same radiation dose had the strongest inhibition rate in all the groups, which demonstrated the necessity of MH for loading H₂PtCl₆, laying a foundation for clinical application and transformation. It may be related to the following factors: (1) MnO₂ had the effect of radio-sensitization. (2) HA had the function of transforming M2 phenotype TAMs into M1 phenotype TAMs, thereby reducing the resistance of tumors to chemotherapy.14 (3) MHP was more susceptible to be absorbed or associated with cell membranes.

We then assessed whether MH-loaded H2PtCl6 increased the apoptosis-inducing effect on HCT-116 cells (Fig. 4b and c). The findings manifested that MH can slightly induce cell apoptosis. Whether early or late apoptosis, the proportion of cells induced by MHP was similar to that of radiation (5 Gy), while being greater than that of MH. Moreover, MHP combined with radiation induced the largest proportion of apoptotic cells in all the groups. Therefore, we speculated that the apoptotic induction of MHP may be one of the reasons for its cytotoxicity.

Several studies have shown that MnO2 can consume endogenous H₂O₂ in the TME²⁶⁻²⁹ and consistently produce oxygen to overcome hypoxic environments, and also attenuate the resistance of radio-chemotherapy.³⁰⁻³² In the present study, Cy3-labeled γ-H2AX antibody was used to reflect double-strand breaks in DNA (Fig. 4d). Different groups, including control, MH, RT alone, and MHP, showed no obvious DNA breaks. Compared with the MH or MHP group, the MH + RT group and MHP + RT group had a significantly higher percentage of cells with DNA strand breaking (Fig. 4e), indicating that both MH and MHP had satisfactory radio-sensitization.

2.5 In vivo MRI and fluorescence (FL) imaging

Given their biodegradability and T_1 -weighted MRI capabilities, MnO₂ NPs were chosen as the carriers of a nano-integrated diagnostic and therapeutic platform. HCT-116-tumor-bearing mice were injected with MHP nanoparticles (5 mg kg⁻¹) through their tail vein. Then, T_1 -weighted MRI images were acquired at different time points (Fig. 5a). The signal intensity of both groups similarly showed upward, downward, and slow

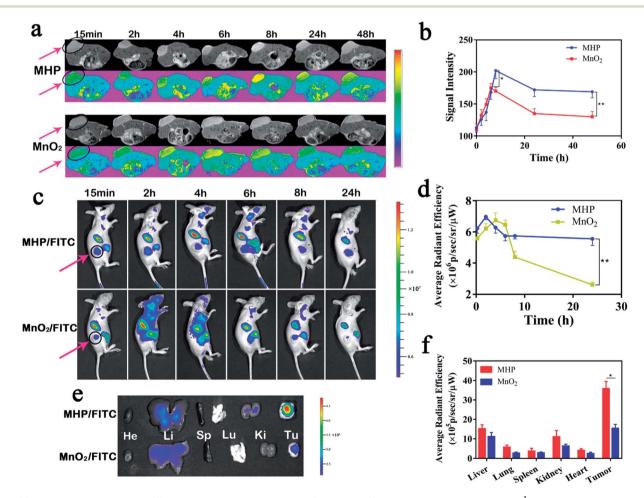


Fig. 5 (a) T_1 -weighted MR images; (b) MR signal intensities of tumors (black circles) in mice injected with 5 mg kg $^{-1}$ MHP or MnO₂ via tail veins, n= 3; (c) fluorescence (FL) imaging; (d) average radiant efficiency in tumors (black circles) calculated at different time points after i.v. injection of MHP/Cy5.5 or MnO₂/Cy5.5 in HCT-116 tumor-bearing mice, n = 3; (e) FL imaging; (f) average radiant efficiency in vital organs of mice and tumors at 48 h following MHP/Cy5.5 or MnO₂/Cy5.5 treatment (He: Heart, Li: Liver, Sp: Spleen, Lu: Lung, Ki: Kidney, Tu: Tumor), n = 3. *P < 0.05; **P < 0.01.

decline trends, while the peak value and the steady-state value after 48 h in the MHP group were higher than those in the MnO₂ group. Afterwards, MHP and MnO2 were labeled with equivalent Cy5.5, and the metabolism and distribution of MHP and MnO₂ in mice were determined by FL imaging (Fig. 5c). Within 24 h, the average radiant efficiency in the MHP group was notably higher than that in the MnO₂ group (Fig. 5d). The mice were sacrificed after 48 h and the tumors and organs were removed (Fig. 5e), in which the retention of MHP in tumors was higher than that of MnO2, and there was no significant difference between them in the main organs (Fig. 5f). On the one hand, the EPR effect of MHP was found to be stronger than that of MnO₂ NPs, which might be related to the superior hydrodynamic stability of MHP, and HA also played a substantial role in tumor binding in vivo. On the other hand, due to the metabolic properties of MHP, the accumulation in the main organs was limited.

2.6 In vivo penetration and combination therapy

In addition to using the MCS to study the penetration of NPs, we also assessed *in vivo* penetration by co-localization percentage of a vascular marker, namely CD31 (red) and FITC-labeled NPs (green). Moreover, MnO₂ NPs/FITC and MHP/FITC (5 mg kg⁻¹)

were injected into tumor-bearing mice via the tail vein, and tumor tissues were collected after 24 h, and then frozen tissue sections were examined by CLSM (Fig. 6a). In the MHP group, there was less co-localization between NPs and blood vessels, while more yellow appeared in the MnO₂ group. On the one hand, it was revealed that MnO₂ NPs had limited penetration ability because of their large particle size and physical properties and could easily aggregate and precipitate, and the majority of them remained on the vascular wall. On the other hand, due to oxidation–reduction reactions of MHP in the TME, once the tumors were entered, MHP released USNPs (\sim 20 nm), which resulted in an excellent interstitial penetration.

As MRI and FL imaging *in vivo* showed that MHP had a promising EPR influence, we further studied the anti-cancer effect of MHP combined with radiotherapy *in vivo*. MH and MHP (5 mg kg $^{-1}$) were injected into HCT-116-tumor-bearing mice *via* the tail vein. After 8 h, 5 Gy radiation was carried out on the tumor site. After this, the volume of tumors was monitored every other day for 14 days (Fig. 6c). The mice in the control group grew faster, and the volume of tumors in the mice on the 14th day was about 9 times higher than that at the beginning. The MHP + RT group (about 1.07 times) showed the best tumor

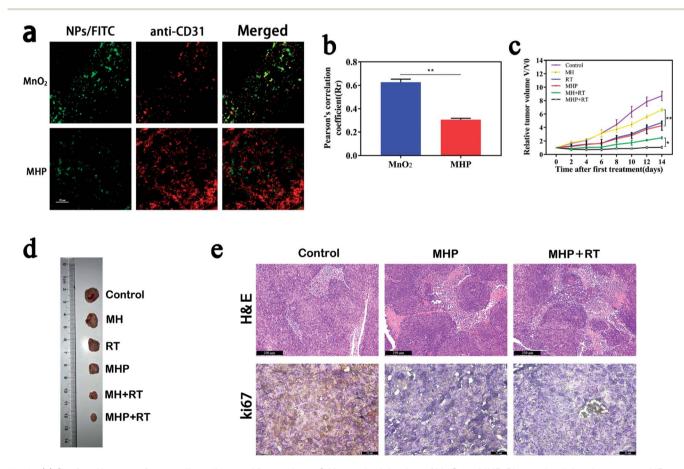


Fig. 6 (a) Confocal images of tumor slices dissected from mice at 24 h post i.v. injection of MnO₂ or MHP. Blue and red signals represent NPs and anti-CD31-stained blood vessels, respectively. Scale bar: 50 μ m; (b) the Pearson correlation coefficient (R_r) calculated in the image, as shown in (a); (c) tumor growth, n=5; (d) representative tumor images on day 14th; (e) images of hematoxylin and eosin (H & E) staining and Ki67 immunohistochemical staining on the 3rd day post therapy. Scale bar: 250 μ m (H & E); 25 μ m (Ki67). *P < 0.05; **P < 0.05.

Paper

suppression effect. Fig. 6d illustrates tumor entities in each treatment group obtained on the 14th day.

To further perceive the inhibitory influence of MHP combined with radiotherapy on tumor growth, hematoxylin and eosin (H & E) staining and Ki67 immunohistochemistry (Fig. 6e) were carried out in tumor tissues on the 2nd day after treatment, and it was revealed that distinct tissue necrosis and Ki67 expression decreased in both the MHP group and MHP + RT group.

Blood testing and histological examinations

There was no aberration in mice during the entire post-treatment period. Although a small amount of MHP was accumulated in the liver and kidneys after injection *via* the tail vein, the targets of the blood routine and blood biochemical values on the 1st and 7th days after treatment are shown in Fig. 7a. Besides, the white blood cell (WBC), red blood cell (RBC), hemoglobin (HGB), platelet count (PLT), alanine aminotransferase (ALT), aspartate aminotransferase (AST), blood urea nitrogen (BUN), creatinine (CREA), mean corpuscular hemoglobin concentration (MCHC), hematocrit (HCT), mean corpuscular volume (MCV), mean corpuscular hemoglobin (MCH), mean platelet volume (MPV), and platelet distribution width (PDW) showed no significant difference compared with the control group. Additionally, 48 h post-treatment, H & E staining of the main organs of the mice showed no significant

damage compared with the control group (Fig. 7b). Mice treated with radiotherapy slightly lost weight at the beginning, but recovered rapidly later (Fig. 7c). These results demonstrated that MHP may be a relatively safe nano-drug in the short term, and further in-depth toxicity assessments should be carried out in the future.

3 Experimental testing

Materials

HA (10 K) was purchased from Lifecore Biomedical LLC (Chaska, MN, USA); H2PtCl6·6H2O was provided by Macklin (Shanghai, China); Cy5.5 was purchased from Meilunbio (Dalian, China). Moreover, a cell counting kit-8 (CCK-8) was purchased from Dojindo Molecular Technologies, Inc. (Kumamoto, Japan); γ-H2AX human anti-rabbit antibody was provided by Arigo Biolaboratories Inc. (Hsinchu, Taiwan); an Annexin V-FITC/PI apoptosis assay kit was purchased from TransDetect (Beijing, China); and Ki67 human anti-rabbit antibody was provided by Affinity Inc. (New York, NY, USA).

Synthesis and characterization of MnO2 NPs 3.2

The synthesis of MnO2 NPs was conducted as previously described, which was slightly modified accordingly. 33 Firstly, 0.1 g KMnO₄ was added to 50 mL ultra-pure water and stirred for 10 min to be fully dissolved. Furthermore, 35 µL oleic acid was

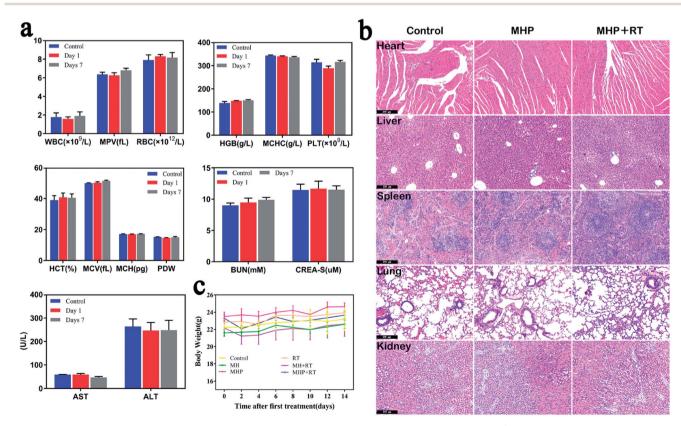


Fig. 7 (a) Blood routine and biochemical tests on the 1st and 7th days after i.v. injection of MHP (5 mg kg $^{-1}$) in female nude mice, n = 5; (b) H & E staining images of major organs (heart, liver, spleen, lungs, and kidneys) at 48 h after i.v. injection of MHP or MHP + RT (5 mg kg $^{-1}$, 5 Gy). Scale bar: 250 μ m; (c) body weight monitoring of HCT-116-tumor-bearing mice every other day post-treatment, n=5.

Nanoscale Advances

added to the solution and stirred for 20 h at room temperature. The color of the solution changed from dark purple to brown black, suggesting that Mn⁷⁺ was reduced to Mn⁴⁺. The colloidal solution was centrifuged for 8 min at room temperature at 8000 rpm; the supernatant was taken and centrifuged for 8 min at 15 000 rpm, and the precipitate was taken and washed five times with 75% ethanol using ultrasonication. Finally, at a constant temperature of 60 °C, TEM, EDS, UV-Vis-NIR, and DLS (Malvern) were utilized for detection.

3.3 Synthesis and characterization of MnO₂-HA (MH) and MnO2-HA@H2PtCl6 (MHP)

Synthesis of MH and MHP was performed based on the laver-bylayer (LBL) method. For this purpose, firstly, the pre-synthesized MnO₂ NPs were added to a certain amount of ultra-pure water and treated using an ultrasonic cell breaker (amplitude: 35%) for 30 s × 5 times. Secondly, HA and chloroplatinic acid with a certain mass ratio were added; the colloidal solution was subjected to ultrasonication 30 s \times 3 times under the same conditions, and stirred for 8 h. Afterwards, it was centrifuged at 15 000 rpm for 8 min to obtain a precipitate. Finally, this was washed with ultra-pure water and dried at a constant temperature of 60 °C to achieve MH and MHP. TEM, DLS, ICP-MS and UV-Vis-NIR were used for detection as well.

3.4 Cellular experiments

To explore the ability of MHP to penetrate into tumors, we produced HCT-116 multicellular spheres. 34,35 Briefly, the bottom of a 6-well plate was covered with 0.5 mL agarose liquid (1.5 w/ v%), after being cooled at room temperature, and a layer of agaropectin was formed on its surface. Then, 3×10^5 HCT-116 cells and medium were co-incubated in each well for about 12 days, in which the suspension was mixed with 1 mL pipettes every 3 days. The same amount of FITC-labeled NPs (20 μg mL⁻¹ of MnO2) was added to the approximate equal amount of multicellular spheres for 6 h. Additionally, HCl and H₂O₂ were used to adjust the experimental conditions. The CLSM was used to observe the results. Cellular uptake was herein conducted as follows: 3×10^5 HCT-116 cells were seeded in a glass-bottom culture dish. MnO₂ NPs/FITC, MH/FITC, and MHP/FITC (20 μg mL⁻¹ of MnO₂) were incubated for 6 h. Green represents FITClabeled NPs and blue represents the nucleus. Then, the findings were observed with a laser confocal microscope. Cytotoxicity assay: 3×10^3 HCT-116 cells were seeded into 96-well plates and incubated for 24 h. Micro-amounts of sterile paraffin were used to cover the surface of the culture medium for 12 h in order to provide an appropriate hypoxic environment. Afterwards, MH, H_2PtCl_6 , and MHP (MnO₂/ $H_2PtCl_6 = 50/17.5 \mu g mL^{-1}$) were added to the culture medium in the presence of paraffin, respectively. After 12 h, 0/2/4/8 Gy of radiation were given, the old medium was removed from the 96-well plate, and fresh medium was added for another 72 h. Relative cell viabilities were analyzed by the CCK-8 assay. Detection of double-strand breaks in DNA was performed as well: MH, H₂PtCl₆, and MHP $(MnO_2/H_2PtCl_6 = 50/17.5 \mu g mL^{-1})$ were added into a glassbottom culture dish containing pre-seeded HCT-116 cells.

Radiation (5 Gy) was given after incubation for 8 h. Then, incubation was followed for another 30 min. Red represents Cy3 labeled double-strand breaks in DNA, and blue represents DAPI. A laser confocal microscope was utilized for visualization.

3.5 In vivo MR and FL imaging

All animals were purchased from the Animal Experimental Center of Xiamen University (Xiamen, China) and were used in accordance with the Institutional Animal Care and Use Committee (IACUC) and approved by the Ethics Committee of the Xiamen University. Moreover, 5×10^6 HCT-116 cells mixed with Matrigel were subcutaneously injected into female BALB/c nude mice. For FL imaging, MnO₂/Cy5.5 and MHP/Cy5.5 (5 mg kg⁻¹) were injected into HCT-116-tumor-bearing mice (300–350 mm³) via the tail vein. These mice were scanned with an optical imaging system (IVIS Lumina II) at intervals and were executed at 48 h, after which their tumors and main organs were used for FL imaging. For in vitro MRI, MHP solutions with different MnO2 concentrations treated with or without H2O2/GSH under acidic conditions were scanned using a 1.5 T clinical MR scanner at room temperature. The relaxation rate $r_1(1/T_1)$ was accordingly calculated. For in vivo MRI, MnO2 NPs and MHP (5 mg kg⁻¹) were injected into HCT-116-tumor-bearing mice (300-350 mm³) via the tail vein. A MRI instrument (9.4 T; Bruker Corp., Billerica, MA, USA) was used for monitoring as well.

3.6 In vivo penetration

HCT-116 tumor-bearing mice (300–350 mm³) were injected with MnO₂ NPs/FITC and MHP/FITC (5 mg kg⁻¹) through the tail vein, respectively. These mice were executed after 24 h. Tumor tissues were frozen and sliced. Red represents Alexa Fluor 488labeled CD31 antibody and green represents FITC-labeled NPs. A laser confocal microscope was then utilized for visualization.

3.7 *In vivo* combined therapy

HCT-116 tumor-bearing mice (100 mm³) were randomly divided into 6 groups (n = 5). Besides, MH and MHP (5 mg kg⁻¹) were injected into the tail vein, respectively. After 8 h, covering the area with a lead plate except the tumor, mice underwent radiation at a dose of 5 Gy. The volume of tumor ($V = \text{length} \times$ width²/2) and body weight of these mice were recorded by every other day post-treatment for 2 weeks. Then, those mice were executed on the 14th day, and the tumors of the mice were taken out and photographed. Another array of tumor-bearing mice were executed 48 h after treatment. Furthermore, H & E staining and Ki67 immunohistochemical staining were performed.

3.8 Blood testing and histological examinations

Female-nude mice received the same amount of saline and MHP (5 mg kg $^{-1}$) through the tail vein. The values of routine blood and blood biochemical tests were detected after 24 h and on the 7th day, respectively (WBC, RBC, HGB, PLT, ALT, AST, BUN, CREA-S, MCHC, HCT, MCV, MCH, MPV, and PDW). Another array of female tumor-bearing mice received saline and MHP (5 mg kg⁻¹) through the tail vein. Combined with Paper Nanoscale Advances

radiation (5 Gy), these mice were executed at 48 h post-treatment, and major organs (e.g., heart, liver, spleen, lung, kidney) were taken out to carry out H & E staining.

Conclusions

In the present study, we synthesized short-term biosafety MHP as an ultra-small NP (USNP) generator by electrostatic adsorption between MnO₂ NPs and HA, and the chelation between HA and H₂PtCl₆. The maximum loading efficiency of H₂PtCl₆ reached 35%. Saline stable MHP with an appropriate initial size (average: 100 nm) was highly aggregated at the tumor site through the EPR effect and HA targeting, stayed longer, in response to acidic and relatively high H₂O₂ TME conditions, and was rapidly decomposed into numerous USNPs (~20 nm) through supramolecular self-assembly of Mn²⁺, HA, and H₂PtCl₆. Then we preliminarily speculated the chemical formula of USNP: $(Mn)_{4n} (H_2PtCl_6)_n (C_{14}H_{20}NO_{11}Na)_x$. So, MHP could uniformly penetrate into MCSs and solid tumors, and was more conducive to radio-chemotherapy. It also has biodegradability and bioimaging functions that allow use of MRI to monitor drug delivery and scientific radiotherapy program adjustment.

Conflicts of interest

There are no conflicts to declare.

References

- 1 P. Wardman, Chemical radiosensitizers for use in radiotherapy, Clin. Oncol., 2007, 19(6), 397-417.
- 2 L. Tang, X. Yang, Q. Yin, K. Cai, H. Wang, I. Chaudhury, C. Yao, Q. Zhou, M. Kwon, J. A. Hartman, I. T. Dobrucki, L. W. Dobrucki, L. B. Borst, S. Lezmi, W. G. Helferich, A. L. Ferguson, T. M. Fan and J. Cheng, Investigating the optimal size of anticancer nanomedicine, Proc. Natl. Acad. Sci. U. S. A., 2014, 111(43), 15344-15349.
- 3 J. Wang, W. Mao, L. L. Lock, J. Tang, M. Sui, W. Sun, H. Cui, D. Xu and Y. Shen, The Role of Micelle Size in Tumor Accumulation, Penetration, and Treatment, ACS Nano, 2015, 9(7), 7195-7206.
- 4 H. R. Jia, Y. X. Zhu, X. Y. Liu, G. Y. Pan, G. Gao, W. Sun, X. D. Zhang, Y. W. Jiang and F. G. Wu, Construction of Dually Responsive Nanotransformers with Nanosphere-Nanofiber-Nanosphere Transition for Overcoming the Size Paradox of Anticancer Nanodrugs, ACS Nano, 2019, 13(10), 11781-11792.
- 5 R. K. Jain and T. Stylianopoulos, Delivering nanomedicine to solid tumors, Nat. Rev. Clin. Oncol., 2010, 7(11), 653-664.
- 6 C. L. Waite and C. M. Roth, Nanoscale drug delivery systems for enhanced drug penetration into solid tumors: current progress and opportunities, Crit. Rev. Biomed. Eng., 2012, 40(1), 21-41.
- 7 S. D. Perrault, C. Walkey, T. Jennings, H. C. Fischer and W. C. Chan, Mediating tumor targeting efficiency of

- nanoparticles through design, Nano Lett., 2009, 9(5), 1909-1915.
- 8 P. Wardman, L. K. Folkes, S. M. Bentzen, M. R. Stratford, P. J. Hoskin, H. Phillips and S. Jackson, Influence of plasma glutathione levels on radiation mucositis, Int. J. Radiat. Oncol., Biol., Phys., 2001, 51(2), 460-464.
- 9 Y. Zhou, S. Hua, J. H. Yu, P. Dong, F. J. Liu and D. B. Hua, A strategy for effective radioprotection by chitosan-based longcirculating nanocarriers, J. Mater. Chem. B, 2015, 3(15), 2931-2934.
- 10 X. Yang, M. Yang, B. Pang, M. Vara and Y. Xia, Gold Nanomaterials at Work in Biomedicine, Chem. Rev., 2015, **115**(19), 10410-10488.
- 11 R. Brown, M. Tehei, S. Oktaria, A. Briggs, C. Stewart, K. Konstantinov, A. Rosenfeld, S. Corde and M. Lerch, High-Z Nanostructured Ceramics in Radiotherapy: First Evidence of Ta₂O₅-Induced Dose Enhancement on Radioresistant Cancer Cells in an MV Photon Field, Part. Part. Syst. Charact., 2014, 31(4), 500-505.
- 12 G. Song, C. Liang, X. Yi, O. Zhao, L. Cheng, K. Yang and Liu, Perfluorocarbon-Loaded Hollow Bi₂Se₃ Nanoparticles for Timely Supply of Oxygen under Near-Infrared Light to Enhance the Radiotherapy of Cancer, Adv. Mater., 2016, 28(14), 2716-2723.
- 13 F. Klemm and J. A. Joyce, Microenvironmental regulation of therapeutic response in cancer, Trends Cell Biol., 2015, 25(4),
- 14 M. Song, T. Liu, C. Shi, X. Zhang and X. Chen, Bioconjugated Manganese Dioxide Nanoparticles Enhance Chemotherapy Response by Priming Tumor-Associated Macrophages toward M1-like Phenotype and Attenuating Tumor Hypoxia, ACS Nano, 2016, 10(1), 633-647.
- 15 Y. Liu, J. Sun, W. Cao, J. Yang, H. Lian, X. Li, Y. Sun, Y. Wang, S. Wang and Z. He, Dual targeting folate-conjugated hyaluronic acid polymeric micelles for paclitaxel delivery, Int. J. Pharm., 2011, 421(1), 160-169.
- 16 K. Y. Choi, H. Chung, K. H. Min, H. Y. Yoon, K. Kim, J. H. Park, I. C. Kwon and S. Y. Jeong, Self-assembled hyaluronic acid nanoparticles for active tumor targeting, Biomaterials, 2010, 31(1), 106-114.
- 17 H. E. Barker, J. T. Paget, A. A. Khan and K. J. Harrington, The tumour microenvironment after radiotherapy: mechanisms of resistance and recurrence, Nat. Rev. Cancer, 2015, 15(7), 409-425.
- 18 Y. Lou, P. C. McDonald, A. Oloumi, S. Chia, C. Ostlund, A. Ahmadi, A. Kyle, U. Auf dem Keller, S. Leung, D. Huntsman, B. Clarke, B. W. Sutherland, D. Waterhouse, M. Bally, C. Roskelley, C. M. Overall, A. Minchinton, F. Pacchiano, F. Carta, A. Scozzafava, N. Touisni, J. Y. Winum, C. T. Supuran and S. Dedhar, Targeting tumor hypoxia: suppression of breast tumor growth and metastasis by novel carbonic anhydrase IX inhibitors, Cancer Res., 2011, 71(9), 3364-3376.
- 19 S. E. Rademakers, P. N. Span, J. H. Kaanders, F. C. Sweep, A. J. van der Kogel and J. Bussink, Molecular aspects of tumour hypoxia, Mol. Oncol., 2008, 2(1), 41-53.

20 I. Lohse, C. Lourenco, E. Ibrahimov, M. Pintilie, M. S. Tsao and D. W. Hedley, Assessment of hypoxia in the stroma of patient-derived pancreatic tumor xenografts, Cancers, 2014, **6**(1), 459–471.

Nanoscale Advances

- 21 Y. Hao, L. Wang, B. Zhang, D. Li, D. Meng, J. Shi, H. Zhang, Z. Zhang and Y. Zhang, Manganese dioxide nanosheetsbased redox/pH-responsive drug delivery system for cancer theranostic application, Int. J. Nanomed., 2016, 11, 1759-1778.
- 22 L. Meng, Y. Cheng, S. Gan, Z. Zhang, X. Tong, L. Xu, X. Jiang, Y. Zhu, J. Wu and A. Yuan, Facile Deposition of Manganese Dioxide to Albumin-Bound Paclitaxel Nanoparticles for Modulation of Hypoxic Tumor Microenvironment To Improve Chemoradiation Therapy, Mol. Pharmaceutics, 2018, 15(2), 447-457.
- 23 Y. Feng, D. Ding, W. Sun, Y. Qiu, L. Luo, T. Shi, S. Meng, X. Chen and H. Chen, Magnetic Manganese Oxide Sweetgum-Ball Nanospheres with Large Mesopores Regulate Tumor Microenvironments for Enhanced Tumor Nanotheranostics, ACS Appl. Mater. Interfaces, 2019, 11(14), 37461-37470.
- 24 J. Shi, R. Ma, L. Wang, J. Zhang, R. Liu, L. Li, Y. Liu, L. Hou, X. Yu, J. Gao and Z. Zhang, The application of hyaluronic acid-derivatized carbon nanotubes in hematoporphyrin monomethyl ether-based photodynamic therapy for in vivo and in vitro cancer treatment, Int. J. Nanomed., 2013, 8, 2361-2373.
- 25 T. H. Tran, J. Y. Choi, T. Ramasamy, D. H. Truong, C. N. Nguyen, H. G. Choi, C. S. Yong and J. O. Kim, Hyaluronic acid-coated solid lipid nanoparticles for targeted delivery of vorinostat to CD44 overexpressing cancer cells, Carbohydr. Polym., 2014, 114, 407-415.
- 26 C. R. Gordijo, A. Z. Abbasi, M. A. Amini, H. Y. Lip, A. Maeda, P. Cai, P. J. O'Brien, R. S. DaCosta, A. M. Rauth and X. Y. Wu, Design of Hybrid MnO₂-Polymer-Lipid Nanoparticles with Generation Tunable Oxygen Rates and Tumor Accumulation for Cancer Treatment, Adv. Funct. Mater., 2015, 25(12), 1858-1872.
- 27 W. Fan, W. Bu, B. Shen, Q. He, Z. Cui, Y. Liu, X. Zheng, K. Zhao and J. Shi, Intelligent MnO₂ Nanosheets Anchored

- with Upconversion Nanoprobes for Concurrent pH-/H2O2-Responsive UCL Imaging and Oxygen-Elevated Synergetic Therapy, Adv. Mater., 2015, 27(28), 4155-4161.
- 28 H. Fan, Z. Zhao, G. Yan, X. Zhang, C. Yang, H. Meng, Z. Chen, H. Liu and W. Tan, A smart DNAzyme-MnO₂ nanosystem for efficient gene silencing, Angew. Chem., Int. Ed. Engl., 2015, 54(16), 4801-4805.
- 29 C. He, D. Liu and W. Lin, Self-assembled core-shell nanoparticles for combined chemotherapy and photodynamic therapy of resistant head and neck cancers, ACS Nano, 2015, 9(1), 991-1003.
- 30 K. F. Xu, H. R. Jia, Y. X. Zhu, X. Y. Liu, G. Gao, Y. H. Li and Wu, Cholesterol-Modified Dendrimers Constructing a Tumor Microenvironment-Responsive Drug Delivery System, ACS Biomater. Sci. Eng., 2019, 5(11), 6072-6081.
- 31 T. D. Eubank, R. D. Roberts, M. Khan, J. M. Curry, G. J. Nuovo, P. Kuppusamy and C. B. Marsh, Granulocyte macrophage colony-stimulating factor inhibits breast cancer growth and metastasis by invoking an antiangiogenic program in tumor-educated macrophages, Cancer Res., 2009, 69(5), 2133-2140.
- 32 C. C. Huang, W. T. Chia, M. F. Chung, K. J. Lin, C. W. Hsiao, C. Jin, W. H. Lim, C. C. Chen and H. W. Sung, An Implantable Depot That Can Generate Oxygen in Situ for Overcoming Hypoxia-Induced Resistance to Anticancer Drugs in Chemotherapy, J. Am. Chem. Soc., 2016, 138(16), 5222-5225.
- 33 H. M. Chen, J. H. He, C. B. Zhang and H. He, Self-assembly of novel mesoporous manganese oxide nanostructures and application in oxidative decomposition formaldehyde, J. Phys. Chem. C, 2007, 111(49), 18033-18038.
- 34 M. A. Oberli, Lipid Nanoparticle Assisted mRNA Delivery for Potent Cancer Immunotherapy, Nano Lett., 2017, 17(3), 1326-1335.
- 35 P. Zhang, J. Wang, H. Chen, L. Zhao, B. Chen, C. Chu, H. Liu, Z. Qin, J. Liu, Y. Tan, X. Chen and G. Liu, Tumor Microenvironment-Responsive Ultrasmall Nanodrug Generators with Enhanced Tumor Delivery and Penetration, J. Am. Chem. Soc., 2018, 140(44), 14980-14989.